

REPORT ON DIAMOND DRILLING

AMI PROPERTY

CLAIM NAMES

GRANT NUMBERS

OM 1-12
TOM 3-24
MI 1-10
BY 1-6

YC07359-YC07370
YC17147-YC17168
YC21051-YC21060
YC28443-YC28448

CLAIM SHEET NO. 115 N-15

LATITUDE: 63° 55'
LONGITUDE 140° 35'

DAWSON MINING DISTRICT


OWNER OF CLAIMS:

GRID CAPITAL CORPORATION, VANCOUVER, BC

BY

H.LEO KING, P.GEO.

Dates of Work: AUGUST 21, 2003 TO SEPTEMBER 4, 2003

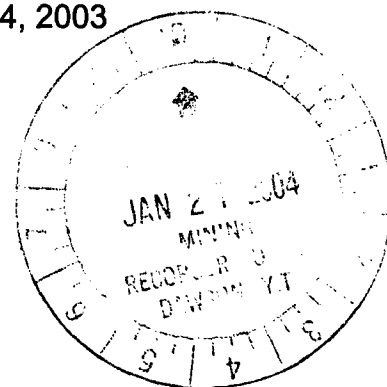

094443

This report has been examined by
the Geological Evaluation Unit
under Section 53 (4) Yukon Quartz
Mining Act and is allowed as
representation work in the amount
of \$ 16,600.

M. B. L.
for Regional Manager, Exploration and
Geological Services for Commissioner
of Yukon Territory.

Costs associated with this report have been
approved in the amount of \$ 16,600
for assessment credit under Certificate of
Work No. 2000476-479

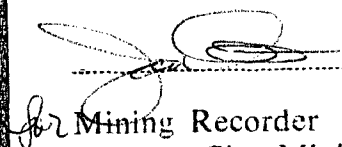

Mining Recorder
Dawson City Mining District

TABLE OF CONTENTS

	PAGE
1.0 Introduction	4
2.0 Property Description & Location	4
3.0 Accessibility, Climate, Local Resources, Infrastructure & Physiography	5
4.0 History	6
5.0 Geological Setting	11
6.0 Deposit Types	12
7.0 Mineralization	13
8.0 2003 work Program	15
9.0 Sample Preparation & Analysis	19
10.0 Conclusions	20
11.0 Recommendations	21
12.0 Statement of Costs	22
13.0 Names & Addresses of Persons & Contractors Employed in Performing the Work & time Employed in Preparing Report	23
14.0 References	24
15.0 Certificate of Author	26

Tables

2.1 List of Claims Being Renewed	3
----------------------------------	---

Figures

Figure 1	Location Map	after pg. 4
Figure 2	Claim Map	after pg. 4
Figure 3	Regional Geology	after pg. 11
Figure 4	Drill Hole Location Map	in pocket

Appendixes

- Appendix A Drill Logs**
- Appendix B Analytical Results**
- Appendix C Certificates of Analysis**

1.0 INTRODUCTION

A diamond drilling program was carried out on the Ami property, located in the Sixty Mile River area, Yukon in August and September 2003. The objective of the drill program was to test coincident induced polarization anomalies and co-incident multi-element geochemical soil anomalies. A geophysical report is filed separately in connection with the Yukon Mining Incentives Program.

The drill program was managed by Bruce Northcote, MSc., under the supervision of H.L.King, P. Geo. The drilling was performed by D.J. Drilling Company Ltd. with field offices at Watson Lake, Yukon.




2.0 PROPERTY DESCRIPTION AND LOCATION

The Ami property is located 60 km WSW of Dawson City, Yukon and centered at Latitude 63° 54' 30" N Latitude and 140° 34' W Longitude within NTS map area 115N/15 (Figures 1). The property consists of 50 contiguous, unsurveyed quartz claims (OM 1-12, TOM 3-24 and MI 1-10, BY 1-6), covering approximately 1045 hectares. The claims are held by Grid Capital Corporation and the diamond drilling was carried out for Grid Capital Corporation.

A sketch of the OM, TOM, MI and BY claims is shown in Figure 2. Claim status is as follows.

Table 2.1 List of Claims Being Renewed
Claim Name **Grant No.**

OM 1-12	YC07359-YC07370
TOM 3-24	YC17147-YC17168
MI 1-10	YC21051-YC21060
BY 1-6	YC28443-YC2844

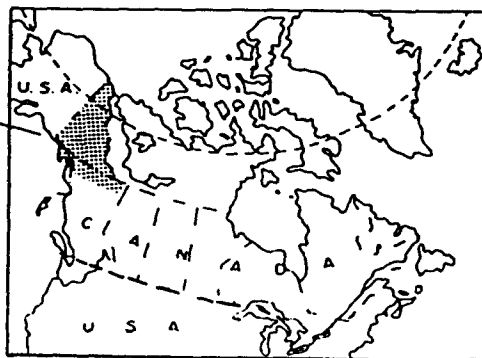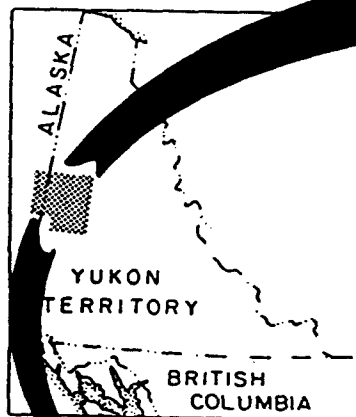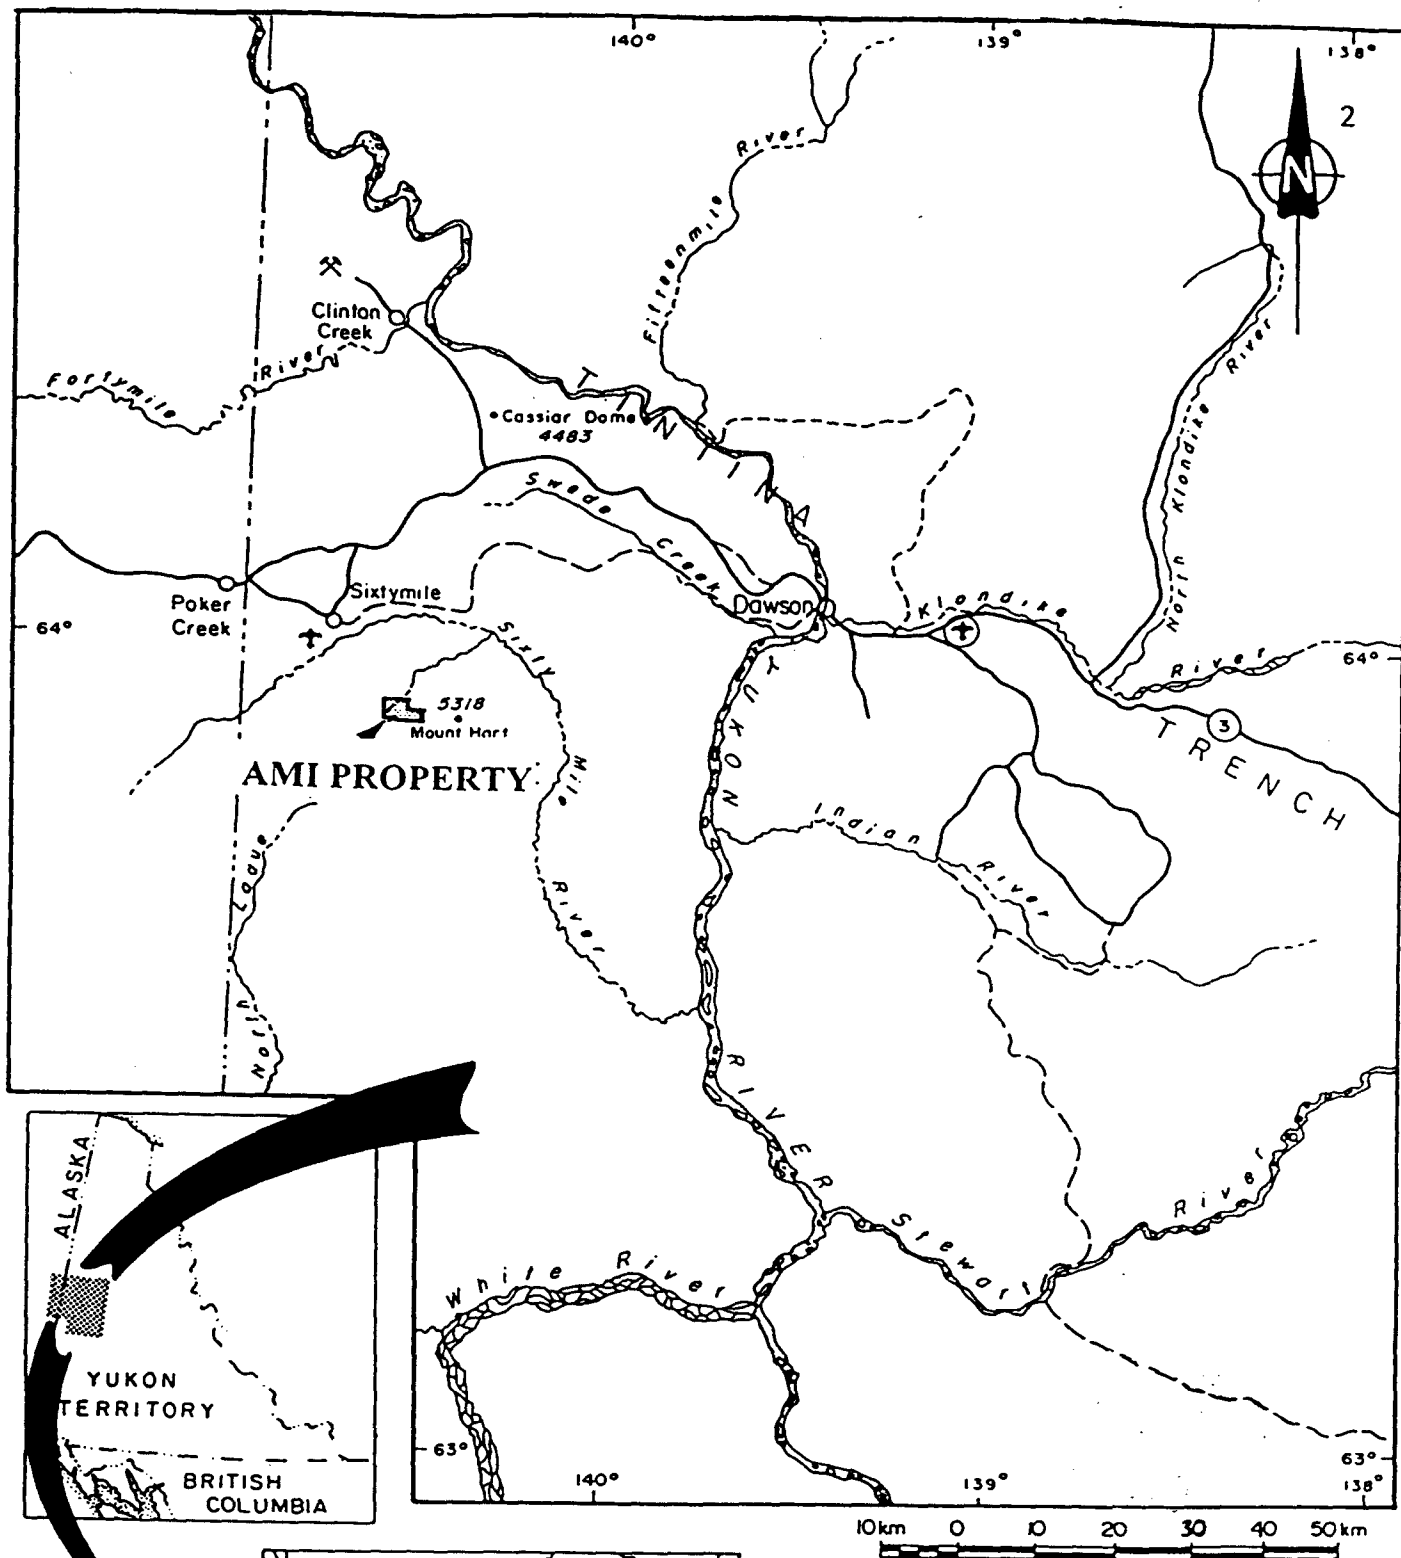

GRID CAPITAL CORP.			
AMI PROPERTY, YUKON			
LOCATION MAP			
SIXTY MILE RIVER AREA, YUKON			
Aurum Geological Consultants Inc.			
	DRAWN BY	SCALE 1:100,000	FIGURE 1
	NH		

CLAIM SKETCH

BY MY OM TOM CLAIMS

CLAIM SHEETS 115N -15

SIXTY MILE RIVER AREA, YUKON

FIGURE 2

CLAIM SKETCH

BY MY OM TOM CLAIMS

CLAIM SHEETS 115N -15

SIXTY MILE RIVER AREA, YUKON

FIGURE 2

CLAIM SKETCH

BY MY OM TOM CLAIMS

CLAIM SHEETS 115N -15

SIXTY MILE RIVER AREA, YUKON

FIGURE 2

CLAIM SKETCH

BY MY OM TOM CLAIMS

CLAIM SHEETS 115N -15

SIXTY MILE RIVER AREA, YUKON

FIGURE 2


CLAIM SKETCH

BY MY OM TOM CLAIMS

CLAIM SHEETS 115N -15

SIXTY MILE RIVER AREA, YUKON

FIGURE 2

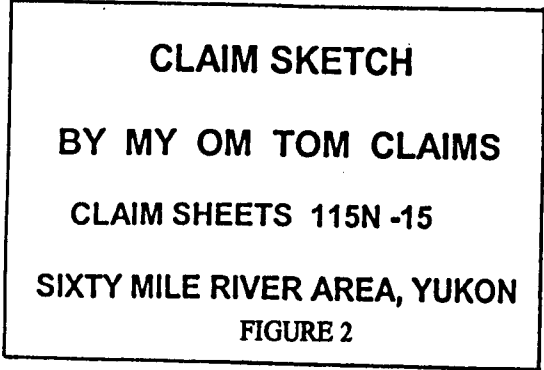



CLAIM SKETCH

BY MY OM TOM CLAIMS

CLAIM SHEETS 115N -15

SIXTY MILE RIVER AREA, YUKON

FIGURE 2

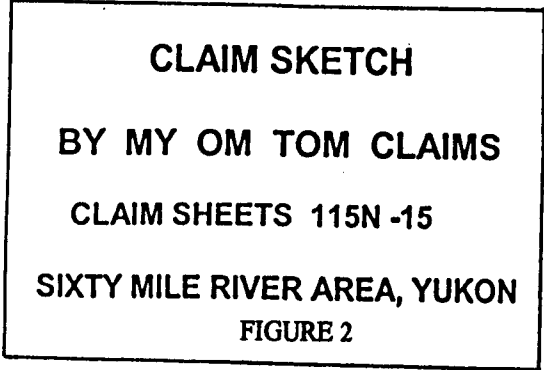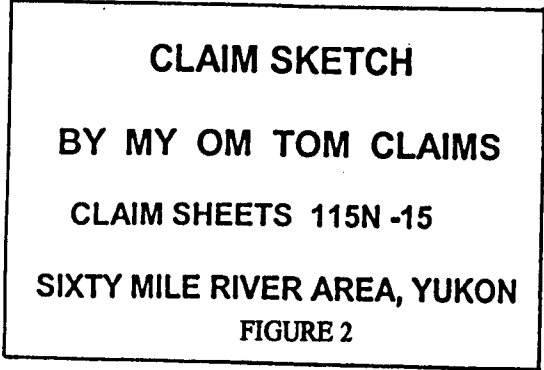

The diamond drilling work was carried out under a Yukon Quartz Mining Act Class II Mining Land Use Permit (Permit No. LQ00104).

3.0 ACCESSIBILITY, CLIMATE, LOCAL RESOURCES, INFRASTRUCTURE & PHYSIOGRAPHY

The Ami property is road accessible. Access from Dawson City is via the paved Top of the World Highway for 88 km to the Sixty Mile Road junction, then by 22 km of gravel road south to the Sixty Mile River and then a further 10 km along the Madsen Creek Road. At this point, a 10 km long, 4-wheel-drive trail leads eastward providing access to the western part of the claim block. The Top of the World Highway west of Dawson City is not maintained during the winter, restricting road access to summer months (May through October).

The property is situated in the partly unglaciated Klondike Plateau. Although Pleistocene glaciation scoured the major drainages in the area such as the Yukon and Sixty Mile Rivers, most of the property escaped the effects of glaciation. Topography is moderately steep, characterized by V-shaped valleys cutting a gently rolling upland. Elevations range from 1000 m at the headwaters of Butler Gulch to 1300 m along the southern edge of the property. Outcrop exposure is very poor (< 1%); however, extensive felsenmeer is common on hilltops and slopes indicating minimal overburden cover.

An interior continental climate is typical of the area with annual precipitation of about 30 cm. The area enjoys short warm summers and cold winters. Permafrost is common, especially on the steeper north and east facing slopes and lower

drainage areas. Most of the property is vegetated with alder and dwarf willow in the higher elevations (>1100m) and stunted spruce and birch in the lower areas.

4.0 HISTORY

The property is near the historic placer gold mining area known as the Sixty Mile River area. Gold was first discovered in the area in 1892 (Cockfield, 1921). Although gold is found in many of the drainages surrounding the property, there has been no significant exploration for lode gold deposits in the property area.

Vein-type silver-lead mineralization on the property was first discovered and staked in 1902. Early development prior to 1911 consisted of shallow shafts and trenches. More recently, in 1964 to 1966, bulldozer trenching was carried out over soil geochemical anomalies about 10 km to the west of the property (Cholach 1969). The area underlying the Ami property was restaked in 1968 by Connaught Mines Limited as part of the Ben and Con claims and soil sampling and bulldozer trenching was undertaken in 1969. In 1974 Connaught Mines Ltd. optioned the property to Shamrock Mines Ltd.

Walhala Explorations Ltd. acquired the property by restaking in 1987 and then optioned the claims to Croesus Resources Inc. who carried out geological mapping and geochemical surveys in 1987 (Keyser, 1988). Exploration work carried out in the area since the 1960's has identified 3 styles of mineralization: 1) silver-lead veins, 2) gold-bearing skarns associated with intrusive contacts, 3) porphyry-style copper-molybdenum mineralization in altered quartz monzonite. All 3 types of mineralization are associated with variable gold values.

A compilation map in the 1993 report by Greg Smith for Tombstone Explorations Ltd. provides the best summary of the 1987 to 1992 work.

In 1987, Croesus Resources Inc. completed soil geochemical surveys that showed strong anomalous results for silver, lead, arsenic, antimony and weak erratic gold associated with the intrusive body. The soil geochemical anomalies cover an area 1 kilometer by 2 kilometers with the main portion located on the current Ami property.

The 1987 exploration program established the existence of skarn type gold mineralization in the area adjoining the OM claims to the west. A garnet-diopside-epidote skarn with locally massive magnetite mineralization was mapped and sampled. Soil geochemistry over the skarn area returned reproducible values of up to 9,090 ppb gold and 23.5 ppm silver.

The Croesus Resources Inc. work determined that the soil geochemistry responded to known silver-lead veins and identified anomalies of the same magnitude in areas where mineralization is not yet known. Mineralized vein float found within the anomalous areas suggest extensions to known veins and new mineralized structures.

The No. 9 Vein is located on the OM claims (OM6 and OM8) that form part of the Ami property and underlies the central portion of a 2 kilometer-long lead-silver-copper anomaly. The vein has been traced by trenching for about 350 meters. Chip sampling across the vein in 1969 (Cholack 1969) returned assays of up to 4.1 g/t gold, 5,697 g/t silver and 52.5% lead over 1.2 meters. The No. 9 Vein is described by Keyser (1988) as "the most unique vein on the property in

that the mineralogy is typified by galena, stibnite and tetrahedrite in a gangue of calcite, barite and minor quartz and clay, and is hosted in quartz monzonite”.

In 1988, Kelan Resources Inc. (Kelan) optioned what is now the Ami property including surrounding claims and carried out a program of geochemical surveys, trenching and 285.3 meters of diamond drilling in 9 holes (Price 1988b).

The geochemical surveys carried out in 1988 and 1989 by Kelan outlined a 2400 m by 300 m area of lead-silver-arsenic-antimony-gold response, in part associated with the magnetite skarn to the west of the OM claims. Soil sampling over the intrusion to the northeast of the skarn in the area underlain by the OM claims, located a large, moderately intense, copper anomaly with two smaller coincident molybdenum anomalies. Trenching failed to reach bedrock and as a result the anomalies were not explained. A linear lead soil anomaly 1300 meters long and 400 meters wide, extending eastward from the area of skarn onto what is now the area covered by the OM claims was outlined. The anomaly encompasses the No. 9 Vein.

The 1988 drilling tested the No. 8 Vein, the magnetite skarn to the west of the OM claims and the No.9 Vein. Six diamond drill holes tested skarn mineralization immediately to the west of the OM claims. The 2 best intersections returned 2, 085 ppb gold across 2.9 meters in Hole K88-8 and 4,055 ppb gold across 1.7 meters in Hole K88-6 (Price 1988b). Three of the holes (K88-1, K88-2, and K88-3) were directed at testing the No. 9 Vein located on the OM 6 and OM8 claims. The drilling encountered zones of potassic, argillic and phyllic alteration in quartz monzonite. Extremely poor core recoveries from

clay altered zones hosting vein mineralization resulted in recovery of only a small amount of vein mineralization. Disseminated and fracture controlled mineralization in wall rocks returned up to 888 ppm copper, 789 ppm molybdenum and 720 ppb gold across 1.5 meters. Lithologies, alteration and mineralization present in this area reflect porphyry-style copper-gold mineralization.

The core from the 1998 diamond drilling program is stored at a site along the road approximately 2 kilometers west of the property.

The property, consisting of the Pra, Har and Bozo claims, was returned to Walhala in 1989 and 7 holes totaling 411 meters were drilled. In 1990, Tombstone Explorations Ltd. purchased the property and carried out a small program of geological mapping and geochemical sampling (Smith, 1992).

The 1992 work was directed at 2 of 7 previously trenched areas that tested soil anomalies of greater than 100 ppm copper within a broad copper anomaly.

A track mounted auger drill was used to obtain samples from 2 of the anomalous areas in 1992. One of the areas is located on what is now the OM 7 claim, the other is located immediately to the west of the OM claims. The auger sampling program totaled 357 feet in 36 holes. The holes ended in the regolith-bedrock contact at depths ranging from 3 to 27 feet. Samples were collected from the bottom of each hole, with random samples midway down selected holes. A total of 40 samples were collected and analyzed for copper and 29 other elements by ICP and a 10 gram assay for gold. The auger drilling tested

an area on what is now the OM 7 claim, near historic Trench No. 5 located immediately to the south of Vein No. 9. The drilling outlined an anomalous area, 400 meters by 150 meters, with greater than 350 ppm copper and up to 26 ppb gold from 23 samples. Copper values averaged 419 ppb copper with a maximum value of 1383 ppm copper. Gold values averaged 8 ppb gold with a maximum of 26 ppb gold. Molybdenum and silver values ranged up to 127 ppm and 2.9 ppm respectively. The anomaly is open in all directions.

A second area, to the west of and bordering the OM 9 claim (Trench No. 3 area), was tested by auger drilling. A total of 17 samples were collected from the Trench No. 3 area. Analytical results ranged up to 550 ppm copper, 40 ppb gold, 36 ppm molybdenum and 7.6 ppm silver.

A portion of the property, consisting of 12 OM and 8 Mug claims, was restaked in June 1998 by Peter Ledwidge and optioned to Carta Resources Ltd. in April, 1999. Carta Resources Ltd. staked an additional 22 claims (TOM Claims) in June and July 1999. An additional 10 claims (MI claims) were staked in September 2001.

Work by Carta Resources Ltd. in June and July 1999 consisted of establishing a base line and grid lines, geological mapping and soil sampling. Total cost of the program was \$18,184.00. The company was subsequently restructured and the claims, including the claims held under option, were transferred to H. Leo King & Associates Inc. on January 18, 2000. Work continued on the property in late August and September 2001 by Doyle Gold Consulting of Dawson City, Yukon for H. Leo King & Associates Inc. The work

consisted of extending the baseline established in 1999 a further 1.2 km to the east and cutting lines to 46E and staking the 10 MI claims.

The soil geochemical survey in-filled and further defined the multi-element anomalies (copper, gold, molybdenum, lead, silver, arsenic) outlined in the 1999 soil sampling program.

5.0 GEOLOGICAL SETTING

Regional Geology

The property is located within the Yukon Tanana Terrane, an assemblage of medium to high-grade, meta-sedimentary and meta-igneous rocks of Paleozoic age that were polydeformed during Early Mesozoic terrane accretion. Pre-accretion, supracrustal rocks are divided into two main assemblages and include locally carbonaceous quartz-muscovite-chlorite schist, quartzite, mafic schist, amphibolite and marble of the Devonian-Mississippian Nasina assemblage and a variety of felsic, cherty schists and non-carbonaceous micaceous quartzite and quartz-feldspar-muscovite schists of the Permian Klondike Schist Assemblage. In the Sixty Mile River district, batholiths of Early Mississippian, granitic orthogneiss occur locally within the Nasina Assemblage (Figure 3). Several large bodies of Early Jurassic, quartz monzonite stocks are also common 10 km SW of the property (Doherty, 2002).

Post-accretion units of Mid to Late Cretaceous age include massive intermediate volcanic flows (correlated with the Carmacks Volcanic Group) and small plugs and stocks of granodiorite and quartz monzonite. Due to the similar

age and close spatial relationship, the volcanic and plutonic rocks are believed to be comagmatic (Mortensen, 1996).

Property Geology

The property is dominantly underlain by a poorly exposed, Late Cretaceous granitic stock intruding intercalated quartzite, chert and marble of the Klondike Schist Assemblage. The stock is primarily classified as a sub-porphyrific, quartz monzonite with local phases of medium grained, biotite granodiorite. However, the contact relationship between the two phases has not been observed in outcrop. Fine-grained intrusive phases are also present along the southern margin of the property (TOM 6) near quartzite felsenmeer, indicating moderate quenching and hornfelsing along intrusive margins during emplacement. Quartzite, intruded by both granodiorite and quartz monzonite, underlies the TOM 22 and TOM 23 claims and extends into the northern MI claims, and may form the northeast margin of the intrusion.

The quartz monzonite stock extends more than 3 km E-W and is 1 to 1.5 km wide. Fracture, fault and sulphide vein orientations internal to the stock also follow a general E-W or WNW strike and imply that initial pluton emplacement and subsequent deformation may be related to major E-W and WNW-striking extensional structures.

6.0 DEPOSIT TYPES

The Ami property is situated within a NW- trending belt of Late Cretaceous intrusives and comagmatic volcanic rocks that extend more than 300 km from the

Carmacks area across the Yukon-Alaska border. This back arc volcanic belt, cutting accreted metamorphic rocks of the Yukon Tanana Terrane, is noted for its copper-molybdenum porphyry and polymetallic vein deposits.

Some of the more significant porphyries include the Casino deposit hosting a resource of 178 MT of 0.3% Cu, 0.028% Mo and 0.38 gpt Au and the Cash deposit hosting a resource of 36MT of 0.17% Cu and 0.018% MoS₂ (Yukon Minfile, 2001). Other significant prospects include the Mt. Nansen and Mt. Cockfield deposits. All of these deposits contain disseminated chalcopyrite and molybdenite within Late Cretaceous to Early Tertiary age subvolcanic rocks.

Also associated with this Late Cretaceous intrusive belt are polymetallic vein systems hosting high grade precious metal values. The NW-trending Webber-Huestis and Brown-McDade vein systems in the Mt. Nansen area consist largely of quartz, arsenopyrite, galena, sphalerite and several silver sulphides. Although the veins are found cutting Lower Paleozoic metamorphic rocks and Early Mesozoic intrusives, they are interpreted to be genetically linked to proximal, Late Cretaceous to early Tertiary age subvolcanic rocks of the Mt. Nansen Group (Tempelman-Kluit, 1981). Proven and probable reserves for the Huestis and Webber veins stand at 85, 727 tonnes of 14 gpt Au and 283 gpt Ag and 58, 524 tonnes at 10 gpt Au and 600 gpt Ag respectively (Yukon Minfile, 2001).

7.0. MINERALIZATION

Two types of mineralization occur on the claims; silver bearing, galena-rich veins and porphyry style copper-molybdenum mineralization.

The No. 9 vein, the most significant, occurs on the OM 6 and 8 claims. The vein, hosted in quartz monzonite, consists of predominantly coarse-grained galena with minor stibnite and tetrahedrite in a gangue of calcite, barite, and minor quartz and clay. The vein strikes at 80° to 100° and dips steeply to the south. Previous trenching has exposed the No.9 vein over a strike length of 350 meters. The vein varies in width from 15 cm to 1.2 m. Initial trench sampling in 1969 returned values of up to 5697 g/t (166 oz/ton) silver, 4.1 g/t gold, and 52.5% lead over 1.2 meters (Cholach, 1969). In 1972, the vein was trenched at regular intervals along a strike length of 350 meters. The best assay was 5500 gpt (160.4 oz/ton) silver, 0.69 gpt gold and 24.8% lead across 30 cm. Three short diamond drill holes were drilled to test the vein in 1988 but due to extremely poor core recovery, only minor vein material was recovered. Coincident silver and lead soil anomalies (> 1 ppm and 100 ppm respectively) extend E-W more than 3 km from the No. 9 vein, supporting the intrusive hosted, easterly striking fracture and vein control identified in trenching.

Another type of mineralization identified in drill core and felsenmeer within the quartz monzonite stock is pyrite, chalcopyrite, malachite and molybdenite, occurring as disseminations, coatings along fractures and in irregular quartz veinlets. Magnetite is disseminated throughout the quartz monzonite stock averaging 1-2% to over 5% in local areas. A broad (1 km by 2 km) copper soil anomaly (>48 ppm copper) coincides with the outline of the western half of the stock, whereas molybdenum anomalies (>5 ppm molybdenum) are restricted to the southeastern margin of the stock, implying that

porphyry style mineralization may be zoned or related to distinct intrusive phases. The 1992 overburden drilling carried out by Tombstone Explorations Co. Ltd. tested two of the copper in soil anomalies identified in the 1960's. One of the anomalies tested was located on claims OM 5 and 7. The shallow auger sampling of oxidized and weathered granitic bedrock produced copper values of up to 1383 ppm copper (Smith, 1993). Much of the geochemically anomalous area remains untested.

8.0 2003 WORK PROGRAM

Line Cutting

During July 3 to July 15, 2003, line cutting was carried out in preparation for geophysical surveys. A total of 19 line-kms were cut and chained with pickets placed at 25m stations.

Geophysical Surveys

An induced polarization (IP) survey was conducted on the AMI property during the period from July 16 to August 2, 2003 by Aurora Geosciences Ltd. of Whitehorse, Yukon. A total of 17.15 line km of surveying was completed and resulted in the delineation of several chargeability anomalies, interpreted to be caused by disseminated sulphides. A report on the geophysical survey is filed as a separate report to comply with the requirements of the Yukon Mineral Incentive Program.

Diamond Drilling

A diamond drilling program to test several selected coincident I.P. and geochemical soil anomalies was carried out for Grid Capital Corporation by D. J. Drilling company Ltd. with facilities located at Watson Lake, Yukon.

The drilling started on August 21, 2003 and was completed on September 4, 2003. Drill holes were located along existing cut and chained grid lines. A total of 813.8 meters of NQ drilling in 5 drill holes was completed for an average drilling rate of 54 m/day including moves. Drill sections are depicted in Appendix A and drill hole locations are shown in Figure 4 (back pocket). The following table lists information regarding the drill holes:

<u>Hole No.</u>	<u>Grid Location</u>	<u>Bearing</u>	<u>Dip</u>	<u>Start Date</u>	<u>Completion Date</u>	<u>Total Length(m)</u>	<u>Over-Burden</u>	<u>Claim#</u>
03-1	16E, 200N	180 ⁰	-50 ⁰	Aug21/03	Aug25/03	182.9	6 m	TOM 11
03-2	12E, 250N	0 ⁰	-50 ⁰	Aug25/03	Aug27/03	203.6	0m	OM6
03-3	8E, 300S	180 ⁰	-50 ⁰	Aug27/03	Aug29/03	196.9	4.3m	OM5
03-4	10E, 240N	0 ⁰	-50 ⁰	Aug30/03	Aug31/03	62.8	0m	OM6
03-5	32E, 580S	180 ⁰	-50 ⁰	Sept1/03	Sept4/03	167.6	3m	TOM6

TOTAL 813.8M

DIP TESTS

<u>Hole No.</u>	<u>Depth</u>	<u>Dip</u>
03-1	100m	-46 ⁰
	182m	-45 ⁰
03-2	188m	-45 ⁰
	203m	-49 ⁰
03-3	103m	-49 ⁰
	196m	-51 ⁰
03-4	62m	-50 ⁰
03-5	167m	-48 ⁰

The core for all 5 holes is stored at a cleared area on Claim OM6.

Following is a summary of the diamond drill logs for hole numbers 03-1 to 03-5. Complete drill logs and sections are found in Appendix A. Analytical results from sections of core that were sampled are tabulated in Appendix B. Drill core from DDH 03-05 was not sampled since only minor amounts of chalcopyrite and molybdenite in disseminated form and sparse veining was intersected.

DDH 03-01

Fine quartz monzonite, weakly porphyritic, generally coarsening with depth. Silicification is fairly pervasive, but weak. Sericitic alteration is more localized and commonly found as vein envelopes. Minor localized K-spar alteration is associated with veining.

Pyrite is finely and weakly disseminated almost throughout the hole. Locally the pyrite is found with pyrrhotite and traces of chalcopyrite. Small veins bearing sulfides are abundant, mostly quartz-carbonate-pyrite, ranging from microveins to approximately 1 cm.

DDH-03-02

Fine to medium-grained, weakly porphyritic quartz monzonite. The top 25 m of core is affected by weathering. Sericite alteration ranges from weak to strong. Silicification is weak and patchy. K-feldspar alteration is minor and localized. Iron staining, limonite, manganese staining and possibly other black secondary mineral coatings are found in the upper, weathered part of the hole. Sulfide mineralization is disseminated and in narrow veins, typically hairline veins

consisting of quartz + pyrite and rarely exceeding 1 cm in width. With pyrite are traces of galena, chalcopyrite, molybdenite and arsenopyrite.

DDH-03-3

The hole starts in weathered medium grained quartz monzonite, enters a short interval of breccia, metabasalt and quartzite, breccia to 24 m, quartz monzonite to 47 m, then breccia consisting of angular clasts of chert, granitic intrusive and chloritized rock fragments. The breccia matrix consists of fine rock fragments, chlorite, pyrite and locally magnetite. Some pyrrhotite, chalcopyrite and arsenopyrite are also noted.

The breccia weakens to quartz monzonite with healed crackle fractures by 91 m, where sulfide mineralization also drops off.

DDH-03-4

Fine quartz monzonite, coarsening to medium-grained near the bottom of the hole. Weathering extends down to approximately 25 m depth, with short intervals of more resistant silicified material. Weak to moderate silicification and sericite alteration continue to the bottom of the hole. Iron staining, limonite, manganese staining and possibly other black mineral surface coatings are found near the top of the hole.

An interval of clay gouge from 37.2 m to 38.0 m contains a massive galena vein approximately 15 cm wide. Much of the gouge has a green colour and contains some fragments of galena. Gouge is limonitic near the crushed quartz

monzonite wall rock. The hole continues in quartz monzonite with minor limonite and sparse fine veins to 62.8 m.

DDH-03-5

The hole intersected medium grained, weakly porphyritic quartz monzonite. Silicification is weak, and sericite alteration is patchy, only locally strong. There is some very minor chlorite. Pyrite is weakly disseminated, only locally reaching approximately 5%. Traces of chalcopyrite and molybdenite are also disseminated. Veining is mainly hairline width or very narrow, with few more than 1 cm wide. They are mainly quartz and pyrite, in some cases with very fine molybdenite. There are a few very sparse Mo-dominated sulfide veins, no more than a few mm wide.

9.0 SAMPLE PREPARATION AND ANALYSIS

All drill core was logged and sections of core containing mineralization were split, placed in plastic bags along with a sample tag, securely tied and shipped to Acme Analytical Laboratories (Acme) in Vancouver, B.C. All core samples were crushed to >75% -10 mesh and then pulverized to >95% -150 mesh.

Samples consisting of disseminated sulphides were treated in the following manner: Fifteen (15) gram splits were placed in bottles and dissolved in aqua regia, a 2:2:2 mixture of HCL, HNO₃ and distilled water (3ml/gm of sample), for one hour at 95 degrees C. The solutions are then diluted to 20:1

ml/gm ratio and then analysed for 36 elements using a Mass Spectrometer. Samples where significant base metal and/or gold and silver values were expected were subjected to fire assay. A 30 gm sample was dissolved in aqua regia and then subjected to ICP analysis. Certificates of analyses are found in Appendix C.

10.0 CONCLUSIONS

The drilling successfully explained the IP chargeability responses and the soil geochemical anomalies targeted. Three of the drill holes (DDH 03-1, 03-2 and 03-5) intersected disseminated sulphides and widely spaced, minor quartz, pyrite +/- chalcopyrite +/- molybdenite veining over core intervals of up to 60m within a weakly altered quartz monzonite representing porphyry-style mineralization. Although anomalous copper and molybdenum values were returned, the values are too low to be of economic interest. DDH 03-3 intersected a wide breccia zone within quartz monzonite with locally up to 20% pyrite and minor disseminated chalcopyrite. The better mineralized sections were assayed for gold but failed to return any significant values.

DDH 03-4 was drilled to intersect a high-grade galena-silver vein at about 50 meters down-dip from its surface expression. A narrow, massive galena vein was intersected at 122 feet (37 meters) down the hole. A fully recovered 0.64 m core interval of the vein returned a weighted average grade of 22.08% lead, 2,086.5 grams/tonne silver and 1.13 grams/tonne gold. The vein, which has been traced for 350 meters on surface, may be of economic interest if greater widths can be identified within the vein structure.

11.0 RECOMMENDATIONS

Several multi-element soil geochemical anomalies remain to be tested for high-grade silver-lead mineralization. Trenching using an excavator may be the best method of exploring the anomalies. Geochemical soil sampling should be extended onto the BY and My claims to determine the full extent of the molybdenum geochemical soil anomaly partially outlined in previous work.

12.0 STATEMENT OF COSTS (July to September 2003)

Line cutting (Coureur des Bois Ltd., Whitehorse)

Travel: Whitehorse to Dawson City, Dawson City to Property	750
Line cutting: 2 men July 3-15/03 and July 24/03	7,700
Camp rental: 14 days @ \$50/day	700

Geophysical Survey (Aurora Geosciences Ltd. Whitehorse)

Camp rental, freight, supplies	1,658
Labour (helpers for geophysics) 2 men July 16 to Aug. 2, 2003	8,500
Mobilization/demobilization	3,400
I.P. Surveying (July 16 to Aug. 2, 2003; equipment plus 2 technicians)	20,550
ATV rental (2 weeks)	700
Food	2,122
Truck & camper rental	3,000
Fuel	635

Drilling (D.J. Drilling Co. Ltd., Watson Lake, YT) Aug. 21 to Sept. 4, 2003

Camp rental (includes mob/demob)	17,094
Cook (14 days)	5,700
Diamond Drilling (direct & indirect costs) 813.8m (NQ)	92,930
Geologist: Bruce Northcote	7,350
Communications	297
Project supervision: H.L.King	1,200
Vehicle rental and fuel	469
Hotel	267
Food	216
Analytical & Assay Costs (Acme Lab, Vancouver)	2,041
Report preparation (8 days)	<u>3,050</u>
	\$180,329

**13.0 NAMES AND ADDRESSES OF PERSONS AND CONTRACTORS
EMPLOYED IN PERFORMING THE WORK AND TIME EMPLOYED IN
PREPARING REPORT**

- 1) Line Cutting Contractor:
Coureur des Bois Ltd.
3 Ryder Place
Whitehorse, Yukon Y1A 5T5
- 2) Geophysical Surveys Contractor:
Aurora Geosciences Ltd.
108 Gold Road
Whitehorse, YT Y1A 2W3
- 3) Diamond Drilling Contractor:
D.J. Drilling company Ltd.
Box 331 Watson Lake YT Y0A 1C0
Or
Box 193-640-26310 Fraser Hwy.
Aldergrove BC V4W 2Z7
- 4) Project Management:
Bruce Northcote
2346 Ashton Road
Agassiz BC V0M 1A0
- 5) Project Supervision:
H. Leo King, P. Geo.
4747 Marguerite Street
Vancouver BC V6J 4H1

Time Spent in report Preparation: **8 days**

14.0 REFERENCES

Cholach, M.S., 1969a; Report on the 1969 Exploration Program in the Sixty Mile River Area, Yukon Territory. Report for Connaught Mines Ltd., Dec. 15, 1969. Assessment Report No. 061130: Department of Indian Affairs and Northern Development.

Cockfield, W.E., 1921; Sixty Mile and Ladue River Area, Yukon. GSC Memior 123.

Doherty, R.A., 2002; Geological Report on the Ami Property, Dawson Mining District, Yukon Territory, Report for Grid Capital Corporation.

Keyser, H.J., 1988; Report on the 1987 Geological and Geochemical Fieldwork on the Golden Crag Property. Assessment Report for Croesus Resources Inc. by Aurum Geological Consultants Inc., April 18, 1988. Assessment Report No. 092511, Department of Indian Affairs and Northern Development.

King, H.Leo, 1999; Report on the 1999 Geological and Geochemical Fieldwork, Ami Property. Report for Carta Resources Ltd.

Mortensen, J.K., 1996; Geological Compilation Maps of the Northern Stewart River Map Area, Klondike and Sixty Mile River Districts (115N/15,16; 115O/13,14 and parts of 115O/15,16. Indian and Northern Affairs Canada, Open File 1996-1(G).

Price, B.J., 1988b; Geological Report , 1988 Diamond Drilling, Butler Gulch Property. Assessment Report for Kelan Resources Inc. and Croesus Resources Inc. November 5,1988.

Smith, Gregory, F., 1993; 1992 Assessment Report on the Sixty Mile Property. Assessment Report for Tombstone Explorations Co. Ltd. by Aurum Geological Consultants Inc. March 19,1993. Assessment Report No, 093094, Department of Indian Affairs and Northern Development.

Tempelman-Kluit, D., 1981; Geology and Mineral Deposits of the Southern Yukon. In Yukon Geology and Exploration 1979-80, Geology Section, Indian and Northern Affairs Canada, Whitehorse.


Yukon Minfile, 2001; Exploration and Geological Services Division, Yukon Region, Indian and Northern Affairs Canada.

15.0 CERTIFICATE OF AUTHOR

I, H. Leo King, P. Geol., do hereby certify that:


1. I am a director of:
Grid Capital Corporation
1075 Duchess Ave.,
West Vancouver, B.C. V7T 1G8
2. I graduated with a Bachelors degree in Geology (B.A.) from the University of Saskatchewan in 1961 and a Masters degree in Geology (M.A.) from the University of Saskatchewan in 1966.
3. I am a member of the Association of Professional Engineers and Geoscientists of British Columbia;
a Member of the Professional Engineers of Ontario;
a Fellow of the Geological Society of Canada;
a Life Member of the Canadian Institute of Mining and Metallurgy;
4. I have worked as a geologist for a total of 41 years since my graduation from university.
5. I am responsible for the preparation of the report titled Report on Diamond Drilling, Ami Property, dated December 9, 2003. I visited the Ami Property from August 8 to August 10, 2003 and from September 5 to September 7, 2003.
6. I have had prior involvement with the Ami Property that is the subject of the Report on Diamond Drilling. The nature of my prior involvement is as a director of Grid Capital Corporation; I was instrumental in the acquisition of the property for Grid Capital Corporation.
7. I am not independent of Grid Capital Corporation. I am a director of Grid Capital Corporation and own shares in Grid Capital Corporation.

Dated this 9th Day of December 2003.

A handwritten signature in black ink, appearing to read 'H. Leo King', is written over a horizontal line.

H. Leo King, P. Geo.

DDH-03-1

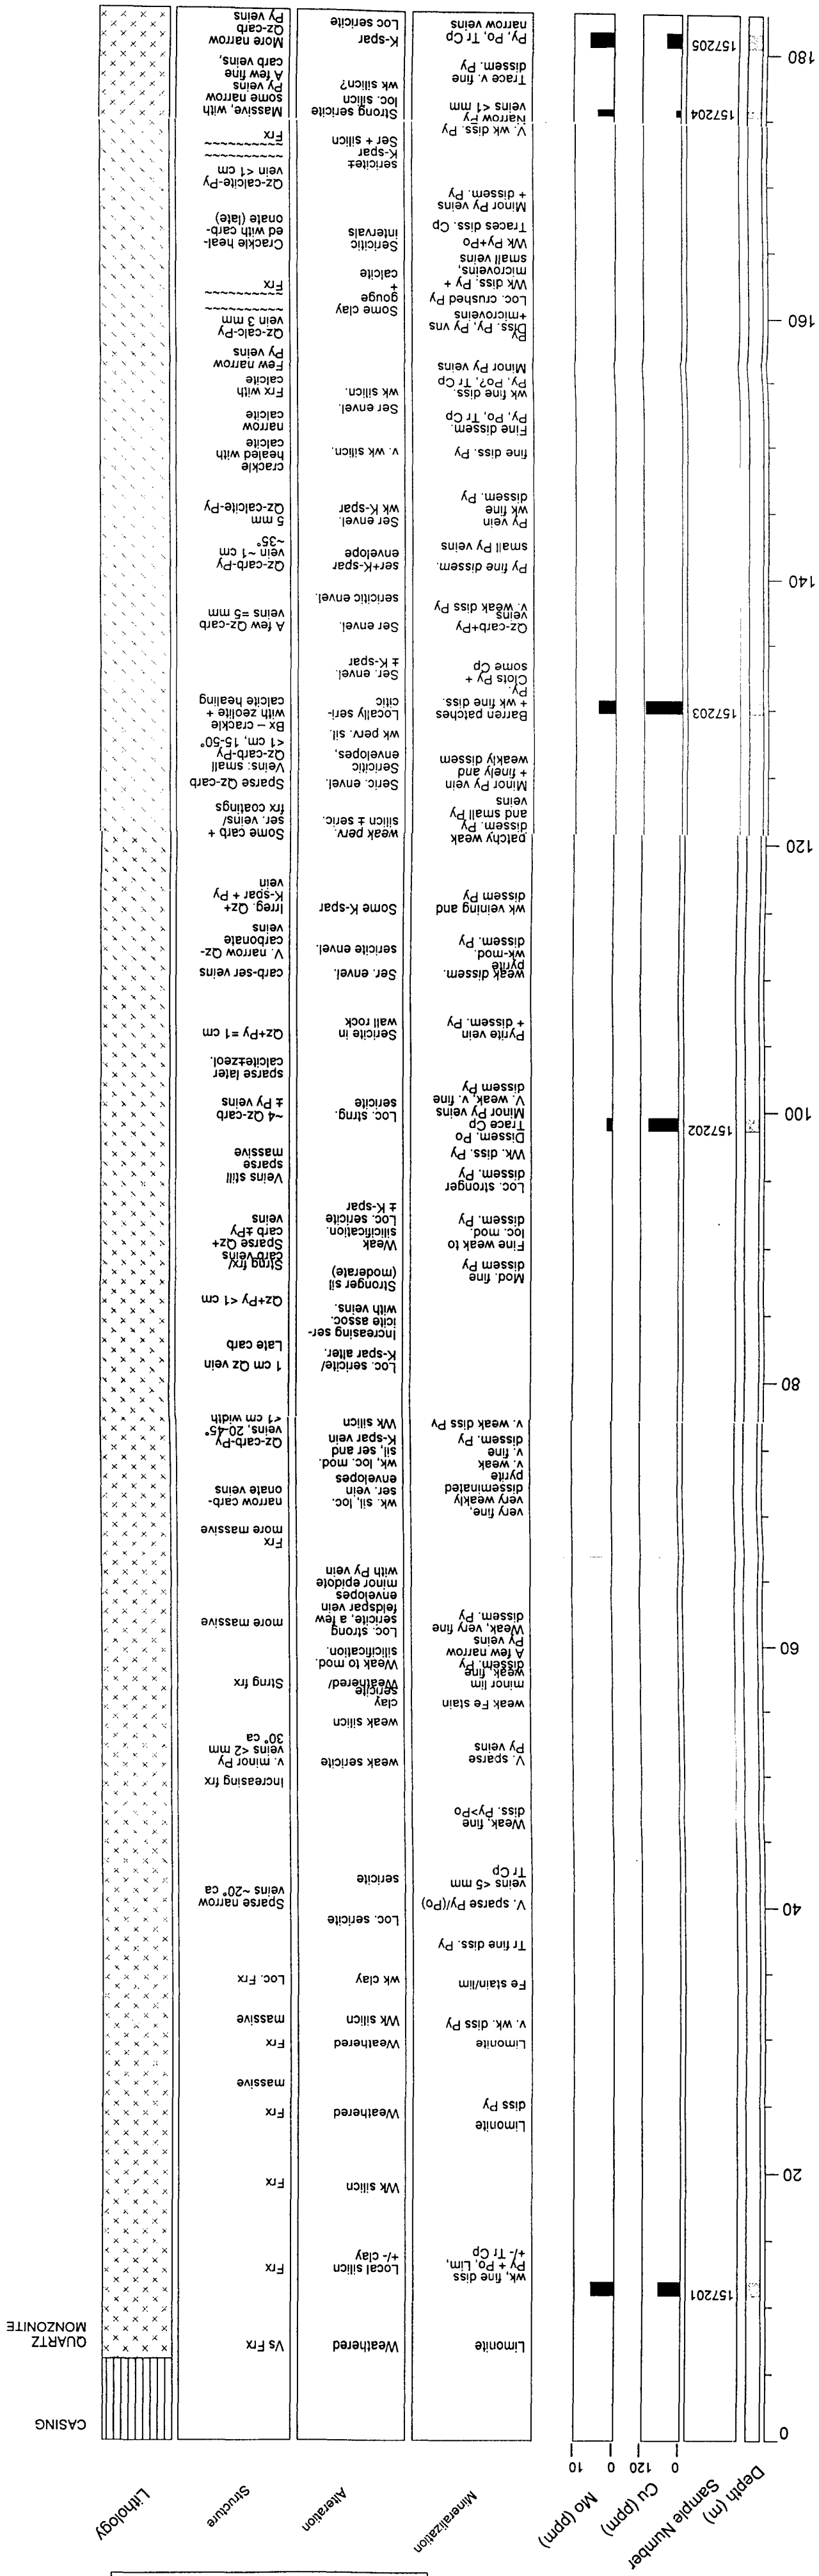

DDH-03-1		Grid Capital Corporation			AMI Project		08/23/03
							Logged by B.K. Northcote
			Collar: L16E 200N -50° south	UTM 07V 521476E 7087080N	Dip tests: 330° 46° 600° 45°		Hole started Aug 21 Proposed depth 200 m (656 ft) Completed Aug 25 600 ft EOH
Depth (ft)	Recovery (%)	Samples	Lithology	Structure	Alteration	Mineralization	Remarks
10							0-20' casing
20	—		Fg intrusive	Vs Frx	Weathered	Lim	Strong weathering, some Fe stain
80							
30	—						
100							
		157201					
		35.5-39					
40	—		Fg QM	FrX	Local silicn +/- clay	wk, fine diss Py + Po, Lim, +/- Tr Cp	Fractured, fine-grained intrusive (Fs, Qz, Bt, Hb). Quartz-rich, looks like granodiorite or granite, but areas of silification to ~1 m with fine disseminated pyrite. Limonite on fracture surfaces. Very minor Mn stain (black) at 57.5'. Silicified biotite quartz monzo +/- sericite.
90							
50	—						
72							
—							
60					Wk silicn		
100				FrX			

	—						
70		Fg QM					
						Lim	
			Frax	Weathered			
80						Diss Py	
	66-117						
	Recovery						
	not		massive				
	measured						
90							
			Frax	Weathered	Lim		
100						V. wk. diss Py	
			massive	Wk silicn			
110		Fine QM				Fe stain/lim	Medium grained quartz monzonite.
			Loc. Frax	wk clay			Some clay + Fe stain near fractures
							(weathering) gets sparser with depth.
							Appearance of sericite envelopes
							associated with pyrite veins at 126.5
							Very weakly porphyritic with sparse
							K-spar phenos ~5 mm
	—						
120						Tr fine diss. Py	
	97						
	—	Fine-med. QM		Loc. sericite			

130				Sparse narrow veins ~20° ca	V. sparse Py/(Po) veins <5 mm Tr Cp	
	100					
	—			sericite		
140	95					Sericite is very weak, but becoming more pervasive(?) Traces Cp with the Py. A few hornblende phenos.
	—					
150	100				Weak, fine diss. Py>Po	
	—					
	92					
160	—			Increasing frx		Some white soft fracture coating: zeolite?
	95			v. minor Py veins <2 mm 30° ca	weak sericite V. sparse Py veins	
170	—					Rock coarsening
	92				weak silicn	Fine – med, weakly porphyritic quartz monzonite
180	—			clay	weak Fe stain	Becomes bleached (clay?) alteration with zeolite fracture coatings
	92	Qz monzon	Strng frx	Weathered/ sericite, loc. silicification.	minor lim weak, fine dissem. Py	Weakly porphyritic, med. grained biotite +/- hb monzogranite or silicified quartz monzonite
190	—			Weak to mod. silicification.		
	100				A few narrow Py veins	

					Loc. strong		
	—				sericite, a few	Weak, very fine	
200			more massive	feldspar vein	dissem. Py		
				envelopes			
	100						
	—						Same quartz monz/monzogranite.
							Overall slight coarsening with depth
210				minor epidote			
				with Py vein			
	100						
	—						
							Pyrite vein □ 1 cm with band of
220			Frz				pale green sericite, pink K-feldspar
							and darker green sericite (not chlorite)
			more massive				
	82						
	—						
230		Quartz Monz	narrow carb-	wk. sil, loc.	very fine,		More conspicuous K-spar phenos
			onate veins	ser. vein	very weakly		to ~1 cm
				envelopes	disseminated		
	96				pyrite		
	—						
240				wk, loc. mod.	v. weak		Still in fine-med. intrusive with
				sil, ser and	v. fine		sparse K-spar phenos to 1 cm,
				K-spar vein	dissem. Py		weak silicification overall, with a few
				envelopes			stronger intervals. Fine dissem Py
	100						is also weak overall, with some Qz-
			Qz-carb-Py				carb-Py veins <1 cm and some
			veins, 20-45°				areas of slightly stronger dissem. Py
			<1 cm width				
	97						
250				Wk silicn	v. weak diss Py		
	—						
	84						
	—						
260	100						

—261.5						
			1 cm Qz vein	Loc. sericite/ K-spar alter. envelope		
	94					
			Late carb veins □ 5 mm			Carbonate-only veins/fracture fillings have no associated wall rock alter- ation.
270	—					
	92			Increasing ser- icite assoc. with veins.		
	—		slight increase in veining			
	83					
	—					
	100					
	—					
280	—		Qz+Py <1 cm (approx 6 veins)			
	95					
				Stronger sil (moderate)		Pyritic veins generally 35-50°
					Mod. fine dissem Py	
			Strng frx/ carb veins			Fractures coated with carbonate and probably zeolite (?)
290	—		fewer frx			
	100	Weakly por- phyritic med. grained QM	Sparse Qz+ carb ±Py veins	Weak but pervasive silicification. Loc. sericite ± K-spar	Fine weak to loc. mod. dissem. Py	Overall, rock is becoming coarser. Still with dissem. Py, pervasive but weak (mod?) silicification, sericite± K-spar alteration envelopes. Med. grained rock is still weakly porph. with K-spar phenos.
	—					
300	—					
						Biotite (hornblende) monzogranite/ silicified quartz monzonite
	86					
	—					
	100			Loc. stronger sericite	Loc. stronger dissem. Py	Coarsening. Possibly silicification becoming weaker and sericite more conspicuous or stronger.
310	—		Veins still sparse	ser/K-spar envelope		
	100					
			massive	weak perv. silicification. and sericit- ization.	Dissem. Py is weak to nil.	Coarser and more massive (few frx)
	—					
320	91				Dissem. Po Trace Cp	
	—	157202	~4 Qz-carb ± Py veins	Loc. strng. sericite		Clot of coarse quartz, Py, Po. minor Cp.
		323.5-326.8	30-50°		Minor Py veins	
						325-327 A few more Qz-carb veins

				<1 cm width			with pyrite and sericitic envelopes
330					ser ± K-spar vein envel.	V. weak, v. fine dissem Py	in wall rock. K-spar alteration is less conspicuous, but still present.
	100						Still some weak pervasive sericite+ silicification. No apparent wall rock alteration associated with carbon- ate + zeolite.
—				sparse later frx/veins with calcite±zeol.			
340							
	98						
—				Qz+Py □ 1 cm ~30°	Sericite in wall rock	Pyrite vein + dissem. Py	
350					weak perv. sericite + Qz		Sericite probably pervasive, as plagioclase has pale greenish color
	100						
—							
360				Some mm scale carb-ser veins	Ser. envel.	weak dissem. pyrite	Little change. Noting some sericite with carbonate in later fractures.
	97						
—				V. narrow Qz- carbonate veins	sericite envel.	wk-mod. dissem. Py	
370							
	98						
—				Irreg. Qz+ K-spar + Py vein	Some K-spar altn of wall rock	wk veining and dissem Py	K-keldspar alteration sparse, except for small vein at 375.8'
380						Py	Some pyrite in fractures without obvious associated wall rock ateration.
	98						
—							
390							
	100						
			Med. Grained sil. Q M				
						patchy weak	Pyrite in very small veins. Not dis-

Sheet1

—			Some carb + ser. veins/ frx coatings (v. narrow)	weak perv. silicn ± seric.	dissem. Py and small Py veins	seminated evenly. Some barren patches.
						390-400' 5 or 6 small (<5 mm wide) Qz, carb, Py veins with sericitic alteration envelopes.
400	100					Similar vein density 400-415'
—						
			Sparse Qz-carb. □ 1 cm	Seric. envel. with K-spar	Minor Py vein + finely and weakly dissem	Some very small pyrite veins without obvious associated wall rock alteration.
410	100		Veins: small Qz-carb-Py <1 cm, 15-50°	Sericitic envelopes, no K-spar		Carbonate-sericite with some of these.
—					Py veins + dissem Py become very	
				wk perv. sil.	sparse	417-423 – brecciation healed with pink mineral (zeolite?) and carbonate probably late stage.
420	100		Bx – crackle with zeolite + calcite healing			
				Locally sericitic	Barren patches + wk fine diss.	
—					Py.	423-428.5 core includes some coarse felsic (pegmatitic) material.
		157203			Clots Py + some Cp	Zone probably roughly parallel to the core. Within this are some clots of pyrite and chalcopyrite.
		425.5-428.8				
430	100					
				Ser. envel. ± K-spar		
—						
440	96					Another short coarse-grained felsic (pegmatitic) zone 439.5-440.5
—			A few Qz-carb veins □ 5 mm	Ser envel.	Qz-carb+Py veins	
450	95				v. weak diss Py	
				sericitic envel. ± K-spar		
—						

Sheet1

460	100		Qz-carb-Py vein ~1 cm ~35°	ser+K-spar envelope	Py +fine dissem. Py	
—		Med QM				
					small Py veins	Py veins < 1 mm wide with carbon- ate, no conspicuous associated wall rock alteration.
	100					
470	—		5 mm Qz-calcite-Py	Ser envel. wk K-spar	Py vein	
	89				wk fine dissem. Py	
—				perv. silicn. v. wk. to absent		
480						
	90		crackle healed with calcite			
—				v. wk silicn.	fine diss. Py	
	100					
490	—					
			narrow calcite veins	wk, perv. silicn?	Fine dissem. Py, Po, Tr Cp	
	100					
500	—		1 Py vein (Qz-calc) 2 mm	Ser envel. Tr epid.		A few bands of sericite alteration (envelopes) one 30 cm wide.
			Frax with calcite	wk silicn.	wk fine diss. Py, Po?, Tr Cp	
	98					
510	—		Few narrow Py veins		Minor Py veins	
	98					Fro 490 to 525 rock is fractured, partly healed with calcite, pink zeolite? Zones of crackling.
			Qz-calc-Py vein 3 mm	10 cm ser envelope	Py	Calcite + most frx post-date the sericite alteration (cut across)
520	—				Diss. Py, Py vns +microveins	Core follows a narrow Qz-carb vein (mm scale) with sericite envel., silicification.
			~~~~~	Some clay gouge		
	97					Crushing in fault at 525' (approx

			Crushed	+		1.5 m wide)
				calcite	Loc. some Py	Faulting probably post-dates most pyrite
			~~~~~		crushed	
				calcite coat-		
530	—		Frx	ing and heal-		
				ing	Wk diss. Py +	
					microveins,	
					small veins	Still in fine diss. pyrite and narrow veining
	95					
540	—		Crackle heal-	Sericitic		
			ed with carb-	intervals	Wk dissem.	
			onate (late)	<0.5 m	Py + Po	Disseminated pyrite locally a bit stronger.
	93				Traces diss. Cp	
				Still weak		
				pervasive		
				silicn.		
				Increasing		
550	—				Minor Py veins	
					+ dissem. Py	
	100		Qz-calcite-Py	envelope		
			vein <1 cm	sericite		
				± K-spar		
				Strong sericite		558-559' 25 cm intense sericite
560	—			sericite±		
				K-spar		
			~~~~~			
			Crushed	clay + calcite		Another fault splay, strongly crushed, only 2-3 ft wide (<1 m)
			~~~~~			
	100					
		Coarse		Ser + silicn		
		Quartz Monz	Frx			567.5' coarser plutonic with K-spar phenocrysts to ~1.5 cm. Alteration is less pervasive.
		porphyry	some carb			
			healing		V. wk diss. Py	
570	—		loc. Qz		Narrow Py	
					veins □ 1 mm	
			Massive, with	Strong sericite		
			some narrow			
	99		Py veins			
		157204	□ 1 mm	loc. silicn		
		575-576.7				
580	—			wk silicn?		
				V. weak,		
			A few fine	if any	Trace v. fine	Mostly massive porphyritic
			carb veins,		dissem. Py	
			1 Qz-carb-Py			
	100		vein ~ 3 mm			
590	—		More narrow			K-feldspar forming irregular veins, patches, several cm wide.
			Qz-carb	K-spar		

Sheet1

				Py veins	Loc sericite	Py, Po, Tr Cp	Seems integral, with diffuse edges.
		157205				narrow veins	Magmatic, or early post mag?
		592-595.5				and weakly	Sparse mineralization.
		97		ser+K-spar	disseminated		
600	E.O.H.						

DDH-03-2

Collar: L12E 250N inclined -50° north

[illegible]

DDH-03-2				Grid Capital Corporation		AMI Project	08/27/03
							Logged by B.K. Northcote
			Collar: L12E 250N -50° north	UTM 07V 521082E 7087102N	Dip tests: 388° 50° 600° 49°		Hole started Aug 25 Proposed depth 200 m (656 ft) Completed Aug 25 668 ft EOH
Depth (ft)	Recovery (%)	Samples	Lithology	Structure	Alteration	Mineralization	Remarks
			Intrus.	Frx			Cored from the top, but with very poor recovery. Drill-milled fragments of
			QM?		weathered	limonite	weathered intrusive with some black
10						Mn stain	manganese (?) stain on surfaces and more pervasive iron.
		12					ps-some of the black coating is not Mn
		157218					Top 200' of hole sampled.
		0-18				other black coating?	
						limonite	
20						manganese	As above
		157219					
		50 18-28					
		157220	QM?	Frx		diss py	Solid piece has some dissem. Py
		18-28				± Po	
						Tr Cp+Ga	
							Better recovery, more solid.
30					short interval		
		60 157221			sericite alteration, very	diss py	Solid pieces with sericite alteration of feldspar phenocrysts.
		28-34			minor silicn.		
		15 157222					Drill-milled and weathered.
		34-39.5					
		39.5					
40			weathered	Frx			
		9 157223	medium				
		39.5-43	grained				
			intrusive			Fe stain,	
			probably			limonite	
		10 157224	quartz		weathered		
		43-48	monzonite				Becoming very friable. V. poor recovery again.
50		12 157225					
		48-52					
		15 157226					
		52-58					
60							Fault
		25 157206					
		58-63					

	25						
		157207					
		63-68					
	—						
70		157208					Clay gouge and disaggregated intrusive. The gouge is iron stained and contains black streaks and patches, some of which are manganese (pyrolusite) others...?
		68-72.3					
			fault	clay gouge	limonitic, with local crushed sulfide		
	100	157228					
		72.3-76					
		157209					
	—	76-79.3					
80		157229					
		79.3-82.2					Fault gouge
			~~~~~				
	100				weak		
		157230			sericite	limonite	Getting out of fault gouge
		82.2-86	Fr	+			
		alt/weath		weathering			
		157210 QM?					
	—	86-89.3				limonite	
90		157231				black surface coating	Drusy cavities in vein roughly parallel to core – yellowish crystals, possibly cerrusite?
		89.3-92.7					
	100	157211	Fr				
		92.7-96				diss py +Po+Tr Cp	
		157232	slightly more massive	weak seric. +silicn.			
	—	96-98.6					
100		157233		+weath.			Core v. fractured, weathered from 98-108'
		98.6-101.5					
	100	157212					
		101.5-104.7	v. minor				
		157213	gouge, few short (10 cm) intervals				
	—	104.7-107.9					
						Fine diss Py	
110		157234	of crushing	sericite +loc. silicn.	+(micro) vns Py, Po, Tr Cp+Ga		Still fractured, less intensely. Silicified interval.
		107.9-111.2					
		157235					
	100	111.2-114.5					
		157236					
		114.5-117					
	—	157214					
		117-120.2	2.5 cm Qz-Ga-Py vein	sericite + silicn.	diss py +Py ± Ga veins		Small vein is banded, multistage. 3 small veins are included in sample over 1 m. 25-45° ca
120		157237	30° ca		small hair-line + Tr Cp		
		120.2-123.5					
	100	157238	Fine-med QM, Bt (Hb) wk porph with K-spar	Fr			Plagioclase replaced by sericite (green spots)
		123.5-126.8					
	—				v. narrow		Py veins (Qz+Py±Ga)
		157239	phenocrysts	hairline	wk silicn	Py veins	

130	126.8-130.1		Py veins			
	157240					Still med-fine QM with sericite alteration
	130.1-133.3		Qz-Py-Ga			of plagioclase ± some chloritization of
		coarsening	~1 cm		irregular	mafic
100	157241		(irreg)	ser/sil	Qz-Py	Very small shear at 135'
	133.3-136.5		~~~~~		Ga vein	
			some			
—	157242		late			Siliceous, becomes softer. Mod-strong
	136.5-139.7		carb	trace		fractures.
140				K-spar		
	157243		Fr _x	vn envel.	Tr Ga,	
	139.7-142.9		(strong)		Tr diss Mo	
				silicn/ser	Py veins	Very local Mo 143.5'
100	157244		minor			
	142.9-146	medium	~~~~~			
		grained	~~~~~			
—	157215	QM	gouge		v. fine	Two small fault splays
	146-149.3		~20°	minor	diss. Py	147.5 and 148'
150			dark Qz +	carbonate	Tr Ga,	Some black ground sulfide
	157245		Py veins	+chlorite		Pervasive sericite alteration gives rock
	149.3-152.5		30-35° ca	on frx	A few Py	a translucent green appearance.
			~5 mm	surfaces	veins <1 cm	
100	157246				Tr Cp	Mineralization in veins is partly crushed
	152.5-155.6		Fr _x			Appears mainly pyrite (some v. fine Ga)
	157216					Chlorite coats many fracture surfaces
—	155.6-159					
160				ser ± silicn		
	157217					Sericite is still pervasive.
100	161.1-164.4					Intensity varies.
	157247			stronger	Few broken	
	163.9-167.3		Intense	silicn.	Py + Qz	
			Fr _x	locally	veins (small)	
—			minor		Tr Cp	
	157248		gouge			
170	167.3-170.6		~~~~~			
			crushed			Some Py veins/microveins/hairline
	157249					
	170.6-173.9					
					coarse Py	
100	157250				Tr AsPy	
	173.9-177.2				Minor Sx	Top vein at high angle to core axis.
			Qz-Py	sericite	Assoc.	Contains minor arsenopyrite.
—			vn 3 cm		with vein	
	157251		Qz vn			Second vein has blue-grey colour.
180	177.2-180.5		1.5 cm			Very fine Ga and/or Mo.
			40° ca			Trace Mo at margin.
	157252					
	180.5-183.8		Fr _x (some	weak seric.	fine	
			carbonate)		hairline	
100	157253				pyrite	
	183.8-187.1				veins	
—						
190			Intense			
			Fr _x			
			crush			
			~~~~~			
	96		crush			

		157254				
	—	195.6-198.9		~~~~~		Minor fault/fault splay.
200			gouge	ser	fine +	Rock coarsening, still with sericite
		157255	crushed		hairline	alteration of plagioclase.
		198.9-202.2	~~~~~		Py veins	
	100		Frx	locally	loc.	
			Locally	stronger	increase	Limonite where strong fractures and
			strong	sericite	in fine	pyrite veins.
	—			weak	Py veins	
				silicn.		
210						Overall, sericite and pyrite are a bit
					increase	stronger.
					fine+	
					hairline	
	100				Py veins	
	—					
220				sericite,	fine Py	
		medium		weak perv	veins	
		-coarse		+envelopes		
		QM				
	100					
	—		Strng Frx			
			Locally			
230			v. strng	V. minor		
			+crushed	K-spar		
	100					
	—		Intense	wk seric.		
			Frx	some		
			~~~~~	carbonate		
240			minor gouge	frx coat		A few short intervals (<10 cm) of fault
			~~~~~			gouge
	100					
	—		more massive	weak		
				pervasive		
				sericite		
250					sparse	
					fine	
					Py veins	
	99					
			massive			
	—					
260			4 mm Qz+Py		slight	
			25° ca		increase	

				minor Py+		in Py	
	100			Qz-Py	local	veins	
				veins	sericite		
					vein		
					envelopes		
	270			Largest			
				Qz-Py			
				~1 cm		Qz-Py	
				80° ca	v. weak		
	97				pervasive		Continuing fine pyrite veins (mostly
					sericite		hairline) with sericitic alteration
					envelopes		envelopes.
					on hair-		
					line veins		
	280						
	100			fine+hair-	Patchy		
				line Py	pervasive		As above.
				+Qz-Py	sericite,		
				veins	mostly		
			medium		envelopes		
			-coarse		on Py vns		
	290		QM			Py becomes	
			not really			very weak	
			porphyritic	calcite			
				vein □ 1 cm			
	100			~10°			
					sericite		Unknown drusy crystalline mineral
				Strng Frx			healing fractures. Suspect zeolite.
				intervals			
	300						
					weak		
					sericite		
	100						
				more			Some limonite fracture coatings
				massive			
	310						
					increasing		
	100			strng	sericite		Mostly hairline veins.
				Frx			
	320			weaker			
				Local			
				Frx			
			QM?				
			masked				
			by strng		interval of		
	100		sericite		strong		
			altn.	sparse	sericite		

—			Qz+Py	alteration		Zeolite (?) filling fractures
330						
	95					
—						
340			Py vein 1.5 cm		Py vein	Coarse pyrite-only vein
			25° ca			
			Fr _x weakening			
	100					
—						
350		weakly porphyritic QM		Patchy pervasive sericite	sparse hairline Py veins	
	95					
			A few Fr _x			
—				sericite weakening		
360						
				diffuse, Patchy silicification	v. weak dissem Py	
	99					
—						
370				weaker silicification with sericite		Alteration is patchy – overall strong sericite.
	98	masked by strng alteration			Fine diss Py	
—						
380						
	98					
—						
390			A few Fr _x Py, Qz+Py veins	strng sericite + silicification	weak diss Py + a few Py veins	Qz+Py veins increase slightly. <5 mm wide, fewer than 5/3 m. Pyrite crystals are large, poikilitic ?

	100						
							Carbonate/zeolite in late fractures
							Sparse K-spar phenocrysts
400	100	Fine-med QM		Patchy sericite + silicn.			
			stronger Fr				
	100						
			Crackle healed with zeol- lite+carb				
410							
	100						
							418-428' blocks jump ahead 10'
420							
	0						
430			crackled, healed w zeol+carb	sericite + Patchy silicification	hairline pyrite + weak fine diss. Py		Crackle fractures and zeolite/carbonate are late, post mineral.
	100						
		Fine-med QM					Quartz monzonite or monzogranite, with sparse K-feldspar phenocrysts.
440				short unaltered interval			
	70			sericite	weak, fine diss. Py + sparse hairline Py veins		
450							Sericite altered Quartz Monzonite
	40	157256	medium	small	silicification mod-strong	increasing	
		454-456.8	grained QM with sparse	Qz+Py ± Ga		veins	3 narrow veins 15' ca at 456'

			phenocrysts		sericite		
460		157257	some > 1 cm	-----	+		
		459.1-461.8		crush	silicification		157257 samples crushed zone
				-----	+		
					local		
	100	157258			minor		
		462.5-465		Qz+Py+Ga vein 1.5 cm	K-spar	Qz+Py+Ga	Some small quartz + Sx veins
	—						Alteration is somewhat patchy, associated with veining (mostly very fine veins)
470							
					increasingly		
					strong		
	100				sericite		
					(pervasive)		
	—						
480							
					hairline vns		
	100				+ diss. Py		
				massive	(weak)		Fairly massive altered QM. Weakly porphyritic, sparse K-spar phenos. Silicified and sericite-altered.
			medium QM		Patchy sericite		
	—			5 mm Qz- carb-Py	minor	Py	
490				25° ca	K-spar envelopes		
				narrow vein 5 mm	mod perv.	Py, Tr Mo	
	100			25° ca	silicn.		A few small Qz ±carbonate Pyrite veins. Trace Mo, possibly v. fine Ga
		157259					
		494.4-496.3		1.5 cm	sericite		
				Qz-Py	vein envel	Py, Tr Mo/Ga	
	—			40° ca	(±K-spar)		
500					local strng sericite	v. weak diss. Py	
	95						
				small			
				~~~~~			
				shear			
	—			60°			508-518' blocks skip 10'
510							
	0						
	—						
520			medium QM	narrow veins (Qz-Carb-Py)	mod perv. silicification +patchy sericite	Fine Qz Py+Tr Ga Poss. Mo?	Very little galena in sparse narrow veins.
	90			Few Frx		minor	


			with carbonate +zeolite	hairline + diss. Py	
530					
	80				
540			v. narrow sparse Qz+Py veins	Py+Tr Ga Tr Mo in veins	Traces of Mo
	100			silicification + patchy sericite	
		medium			
		157260 QM			
	100	545-548	sparse K-spar phenocrysts	fine diss. Py	
550			Fr _x		
		257261			10 cm of gouge
	100	552.5-554.7	crush		Crushing, minor gouge
560					
	100				
		157262	medium	weak, loc mod diss pyrite	
		563.7-565.5	QM		
570			2 cm Qz+Sx 45°	moderate silicification +	2 cm Qz (+carb) vein contains Py, Cp, Mo, Ga, AsPy, Po?, Sph?
	100			Patchy sericite	
			narrow Qz veins	Py	
			Fr _x broken Py+? vein		V. sparse narrow Qz-Py vein
580					
			Fr _x	Patchy sericite	weak Py veins, hair- line + diss
	100		crush	+	pyrite
				silicification	Silicification becoming patchy
590			crush		

		157265		crush			
	100	592.0-595.0		~~~~~			
		157266		2.5 cm		Py, Tr Mo	Qz-Py +Tr Mo in narrow veins
		595.0-597.0	Fine-med	Qz vein			20 cm of gouge
	—	157267	QM	~~~~~			2 short 10-20 cm intervals of gouge
		597.0-599.0					
600				~~~~~			
		157268		broken	sericite		
	100	602.5-603.5		7 mm Qz	silicification		
				vein 15°	some	Qz, Py, Cp	Narrow vein
				Frax	chlorite		
				crush			A few carbonate>quartz veins, al-
	—			Frax			most no mineralization associated
				Qz veins		Qz+Py+Ga	
				to 1 cm		(<5% Ga)	Frequency o quartz veins picking up
							to ~1-2/m
	100			Few Frax			
				Qz veins	sericite	Py-Ga	
		157264		to 1 cm	drops off		Some Galena
		614.5-617.4					
	—				silicification		
					silicification		
	99						
		157269		crush			
		623.0-626.0		~~~~~			
				sparse		Qz-Py±Ga	Veins approx. 1 per m.
	—			Qz-Sx			
				to 1.5 cm			
	100	157270					
		632.2-635.4		fairly	silicification		
				massive		Ga	Minor galena in a 5 mm vein.
		157271	medium				
	—	635.4-638.5	-coarse				
			QM	4 cm	moderate		
			still weakly	Qz vein	pervasive	Py, AsPy, Ga	640' – a 4 cm coarse quartz vein
			porphyritic	~45°	silicification		with 25-30% pyrite, 7-10% arseno-
		157272	with K-spar		local		pyrite and minor galena.
	100	640.2-643.5	phenocrysts		sericite		
		157273			vein		
		643.5-645.0			envelopes		
	—						
		157274		5 mm		Qz, Ga, Sph	
		649.9-652.4		Qz+Sx		Py, Cp	Very minor vein
	97			vein	silicification	minor Cp	Small chalcopyrite vein.
				1 cm Qz		Py, minor	
		157275		vein 30°		Ga, Tr AsPy	

		655.0-657.2					
658 E.O.H.							

**DDH-03-3**

Collar: L8E 300S inclined -50° south

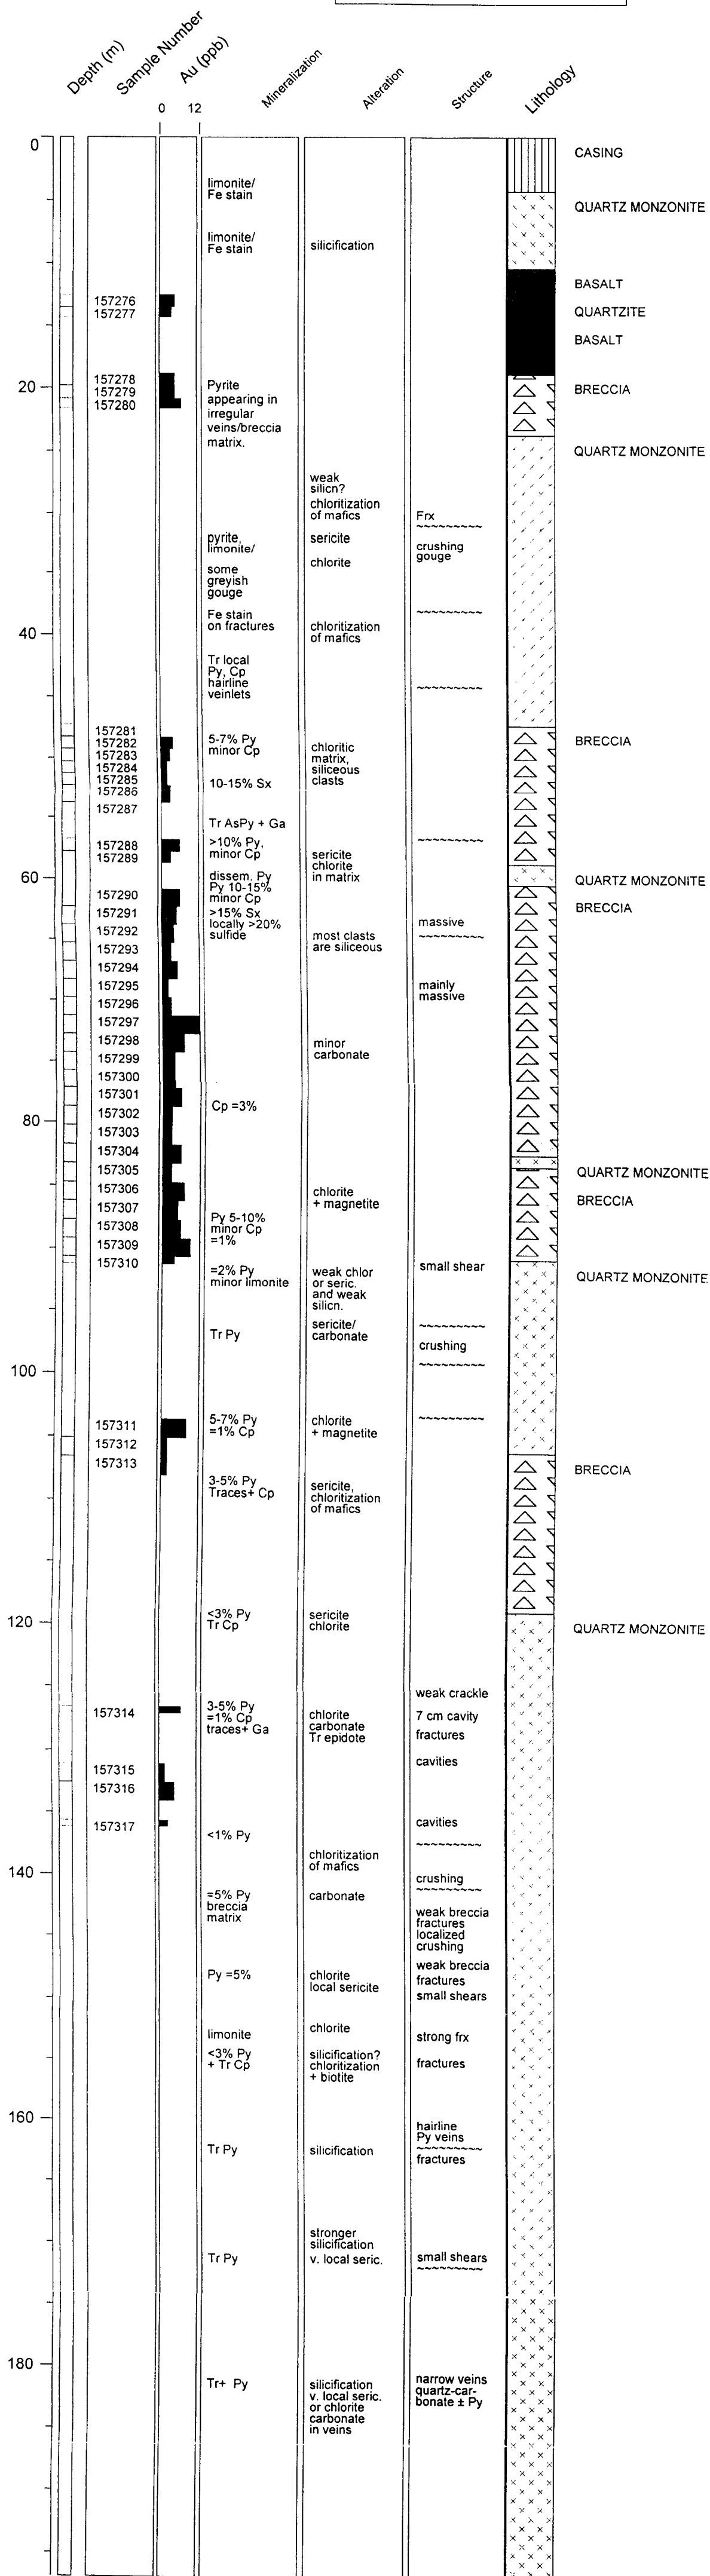

DDH-03-3			Grid Capital Corporation		AMI Project		09/01/03
			Collar: L8E 300S -50° south	UTM 07V 520713E 7086530N	Dip tests: 340' 50° 646' 51°		Logged by B.K. Northcote
							Hole started Aug 27 Proposed depth 200 m (656 ft) Completed Aug 29 646 ft EOH
Depth (ft)	Recovery (%)	Samples	Lithology	Structure	Alteration	Mineralization	Remarks
10						limonite/ Fe stain	0-14' casing

	98	157278	breccia				matrix. Clasts mainly intrusive, with 10-15% consisting of chlorite, pyrite, small lithic fragments, some magnetite, locally minor epidote.
		61.7-65.0					
		157279					
		65.0-68.3					
70		157280					
		68.4-71					
		100					
			breccia				
							Narrow 15 cm zone of crushing
80			QM				
		97					
					weak silicn? (maybe nil)		Quartz Monzonite (coarse). Appears fresh, unaltered except locally, esp. in fault zone.
90			medium to coarse QM				
		95			some chloritization of mafics		
			Frax increase				
100			~~~~~				
		70			sericite locally	pyrite, limonite/	
			intense crushing with intervals of gouge				
110					some chlorite		fault
		93				some greyish gouge	
120							
		100					
			massive, with a few fractures	?		Fe stain on fractures	
			QM				
					some chloritization of mafics		more-or-less fresh QM, some alteration and veinlets

130						
	98					
					Tr local	
					Py, Cp	
					hairline	
					veinlets	
140			stronger			
			fractures			
			v. minor			
	100		~~~~~			
			gouge			
150						
		QM				
	98					
		157281	breccia			
		155-158.3		only a few	5-7% Py	Breccia – angular clasts of: chert, intrusive
				fractures	minor Cp	(silicified and K-spar? altered), chloritized
						rock, other...?
160		157282		chloritic		Matrix of fine rock fragments, chlorite, pyrite
		158.3-161.6		matrix,		magnetite, silica(?), pyrrhotite(?), chalcone
				siliceous		pyrite, locally some minor epidote.
				clasts		
		157283				With the exception of the chloritic fragments,
	100	161.3-164.9				clasts do not appear to be mineralized.
		157284				
		165-168.2				
					10-15% Sx	
170		157285				
		168.2-171.5				
	99					
		157286				
		171.5-176.4				
		157287				
180		176.4-181.3			Tr AsPy + Ga	
						Intrusive clasts are pink, siliceous (v. hard)
						and tend to be larger than the chert clasts
	100		~~~~~	sericite		
					>10% Py,	
			v. minor		minor Cp	
			~~~~~			
		157288	gouge	sericite		
		186.2-189.5				Clasts range up to ~0.5 m
190						
		157289	breccia			
		189.5-192.5				
				chlorite		Mineralization drops off in QM. Looks very
	91			+	traces+	chloritic, but it is very hard, siliceous, mag-
		QM		silicn.	dissem. Py	netic.

	—		breccia		Py 10-15% minor Cp	Back into Bx same as above. Possibly matrix more siliceous?	
200				chlorite + silicn.			
		157290					
	100	199.5-204.4			>15% Sx		
			massive, with few fractures	mainly chlorite in matrix	locally >20% sulfide	Some carbonate with chlorite in matrix.	
	—	157291					
		204.4-209.3					
210				most clasts are siliceous			
		157292					
		209.3-214.2				A few dark, fine-grained clasts: metabasalt?	
	100						
			10 cm ~~~~~				
		157293		shear			
	—	214.2-219.1					
220			few fractures				
		157294					
		219.1-224.0	mainly massive				
	100					Breccia overall seems less siliceous. Most clasts are siliceous, but matrix is soft and chloritic. Only locally more siliceous ?	
		157295					
		224.0-228.9					
	—						
230		157296					
		228.9-233.8					
	100						
		157297					
		233.8-238.7					
	—						
240				minor carbonate		Some carbonate-coated fractures	
		157298					
		238.7-243.6					
	100						
		157299				Clasts contain fine pyrite microveins, hairline veins.	
		243.6-248.5					
	—						
250							
		157300					
		248.5-253.4					
	100						
		157301				Proportion of chalcopyrite picks up locally to ~3%	
		253.4-258.3			Cp □3%		
	—						
260							
		157302					

		258.3-263.2				
	97					
		157303				
		263.2-268.1				
	—					
270						
		157304	QM			Short interval of QM or a large clast. Bx
		268.1-273				dominated by angular clasts of silicified,
						sericitized or K-spar altered intrusive (pink)
	100		breccia			
		157305				
		273-277.9				
	—					Becomes dark, chlorite+magnetite alteration
				chlorite		
				± silicn?		
280		157306		+ magnetite		
		277.9-282.8				
						Dark clasts, breccia looks chloritic, very dark,
						but also hard, siliceous. Suspect chloritic
				local		altered with overprint of silicification? Patches
	100			sericite		are magnetite rich. Locally lighter green, prob-
		157307		+ silicn	Py 5-10%	ably sericitic.
		282.8-287.7		and	minor Cp	
				chlorite	□1%	
	—			+ silicn		
290		157308				
		287.7-292.6				
	100					
		157309				
		292.6-297.5				
			breccia	small shear		Into QM with crackle fractures.
	—	157310				
		297.5-298.5	QM	strongly	weak chlor	□2% Py
300				broken	or seric.	minor limonite
					and weak	
					silicn.	
	90					
	—					
310						
				~60°?	sericite/	
	95			~~~~~	carbonate	
				crushing		
			QM		Tr Py	
	—					
320						
	100					
	—	326.5		~~~~~		
				a few		

			fractures			
330						
	95					
			20 cm			
	100	-----	~~~~~	chlorite	5-7% Py	
		breccia	gouge	+ magnetite	□1% Cp	Dark breccia with chlorite+magnetite, local
340		(QM)				sericite.
		157311				
		339.9-344.8				
	76					
						Short interval breccia
		157312				
		344.8-349.7				
350						Few □1 cm open cavities.
		157313				
		349.7-354.6	weakens			
	100		to crackle		3-5% Py	
			breccia	sericite,	Traces+ Cp	
			in QM	chloritization		
				of mafics		
360				weak		
				silicification		
						Small, open, carbonate-lined cavities
	100					appearing. 1-2 cm.
	100					
370						
						Silicification, if any, is weak.
	100					
380						
	90					
	100					
			breccia			
			weakens	sericite	<3% Py	
390				chlorite	Tr Cp	
				weak		
				silicification		
	100		QM			

400						
	99					
410		QM crackle	weak crackle healed with pyrite, carb- onate and some seric.			Some sericite in fractures. Mafics are chloritized. Minor epidote.
	100				3-5% Py □1% Cp	
			7 cm cavity	chlorite carbonate Tr epidote	traces+ Ga	
		157316 415-416.8				Cavity filled with coarse calcite, pyrite, chal- copyrite, minor galena. Some associated chlorite and epidote.
420			fractures			
	100					
430		QM	cavities in crackled QM			Pink coating on a fracture/cavity. Looks like erythrite
		157314 430-434.9				Cavities with calcite, pyrite, minor chalco- pyrite, Tr+ galena, typically coarse crystals with euhedral terminations. Open spaces to several cm. (driller reported losing water pressure here)
		157315 434.9-439.8				
440						
	95					
		157317 445-446.7	last of the cavities		<1% Py	
450			~~~~~ strong broken local crushing	v. weak silicn/seric.? chloritization of mafics		
	100					
			crushing ~~~~~			

460						
			weak breccia	carbonate chlorite	□5% Py breccia matrix	QM becoming brecciated again, with little dislocation, healed with pyrite, carbonate, some chlorite.
	100					
	—					
470			fractures with very localized crushing			
	100					
	—					
480			weak breccia			Still in breccia with little dislocation. Patches with sericitization of feldspar.
	98	QM breccia?	fractures	chlorite local sericite	Py □5%	
			~~~~~ small shears			Two 10-20 cm shears
	—		fractures			
490						Brecciated quartz monzonite, little dislocation of clasts.
	100					
	—			chlorite +		
500			strong frx	sericite	limonite	
	100					
				silicification? chloritization + biotite	<3% Py + Tr Cp	Short interval of the pink intrusive breccia, now with some dislocation, chloritic matrix with some biotite + quartz.
	—		fractures			
510						508-518' labelled blocks skip 10'
	0					
	—					
520		QM				Breccia ends – core is massive QM. Chloritized mafics with siliceous overprint.
	100		hairline Py veins			

	—			fractures			
				15 cm			
530				~~~~~			
				gouge	silicification	Tr Py	
					(v. minor		
	97	Coarse	fractures	local sericite)			
		QM					
							Harder, more siliceous, coarse QM.
							Generally massive, with some fine
							veining.
	—						
540							
	100						
	—						
550							
					stronger		
					silicification		
	100						
	—			small shears			
560				~~~~~	v. local seric.	Tr Py	
				+ 1 cm Qz			
				carbonate			
				Sx vein			
	100						
	—						
570							
	94						
	—						~~~~~
580							578-588' labelled blocks jump ahead 10'
	0						
	—						~~~~~
590		Coarse QM					
			narrow and				

			hairline			
			veins	silicification	Tr+ Py	Coarse silicified QM
	100		quartz-car-	v. local seric.		Continues to E.O.H. 646'
			bonate ± Py	or chlorite		
				carbonate		Only minor fine veining.
				in veins		
	—					
	600					
	100					
	—					
	610					
	100					
	—					
	620					
	100					
	—					
	630					
	90					
	—					
	640					
	100					
	—					
	55					
646' E.O.H.						

## DDH-03-4

Collar: L10E 240N inclined -50° north

Depth (m)	Sample Number	Pb (%)	Ag (gm/mt)	Au (gm/mt)	Ag Assay Values (gm/mt)	Mineralization	Alteration	Structure	Lithology
		0 65 0-3100 0 1.5							
0						limonite, Mn + other black?	silicn/weath	FrX	QUARTZ MONZONITE
							local weak silicification		
20						Py <2%	weathered	local crushing	
							silicification + sericite	small shear Hairline Py/ Cp veins FrX	
							moderate to strong silicn.	crushed, minor gouge	
	157318 157319 157320 157321 157323	22			0.2 0.8 64.5 3099.4 1770 7.2	green clay massive galena green clay		crushed gouge ~60° 15 cm galena 4 cm Qz vein	15 cm wide massive galena vein at 37.5 m
40							silicification	hairline Sx	
							weak silicification	strong frx	
							moderate silicification moderate sericite	gouge+ crushed Becomes massive moderate	
							moderate sericite weak silicn? sericite	fractures fairly massive crushed	
60							weak silicn	± massive	

DDH-03-4			Grid Capital Corporation			AMI Project		09/03/03
							Logged by B.K. Northcote	
			Collar: L10E 240N -50° north	UTM 07V 520879E 7087087N	Dip tests: 206' 50°		Hole started Aug 30 Proposed depth 60 m (197 ft) Completed Aug 31 206 ft EOH	
Depth (ft)	Recovery (%)	Samples	Lithology	Structure	Alteration	Mineralization	Remarks	
							Cored from the top	
			Fine QM	FrX	silicn/weath	limonite, Mn + other black?	To ~80' the core consists of short drill milled segments of fine silicified quartz monzonite or monzogranite. Fracture surfaces ar iron stained, with some limonite, some manganese staining and possibly other black coating material. Recovery is poor, but improves with depth	
10		7						


—						
	80					
					Fe, Mn stain	
—						
70				weathered	Py <2%	
	83					
—		Fine QM	local crushing		limonite	
	83					
—						
80						
	90					Core forming larger segments
—			small shear at low angle to core axis			1 cm quartz vein in shear
	100		~~~~~			
—		Fine QM				
90			Hairline Py/ Cp veins	silicification + sericite	Tr Py, Cp	
	100				limonite	Limonite in fractures
—			Fr			
100		weakly porphyritic		moderate to strong silic.		
	100					
		Fine QM	~~~~~			105-109' crushed, some gouge Edge 45° ca
			crushed, minor gouge		limonite/ Fe stain	
—			~~~~~			
			crushed			
110				weathered?		
	100		crushed			
		157318			strong limonite	Some black coating on fractures
		114.3-117.6				
—		157319	crushed			
		117.6-120.8				
120		157320				
		120.8-122.4	gouge ~60°			
		157321	~~~~~			
	100	122.4-122.9	vein 50-60°	? green clay	green clay	Galena vein – presumably No. 9 vein.
		157322	15 cm	gouge	galena	Here 15 cm wide (galena-rich portion)
		122.9-124.5	galena		green clay	and in an interval of gouge with green
		157323	~~~~~			color near the galena and rusty near
		124.5-127.8	crushed		strong limonite	crushed wall rock. Gouge+vein 122-124.7
—						

130				weathered?		
					moderate limonite	
	100		strong frx			
			4 cm Qz vein 35° ca		limonite	Quartz vein – drusy.
—						
140			some hairline Sx veins	silicification	Tr malachite Tr Py, Ga	Tr malachite in fractures Py, Ga in fine veins
	100				limonite	Limonite on fracture surfaces.
			strong frx			
—				weak silicification	moderate limonite	
150				?		
	100					
			~~~~~		limonite	
—			gouge+ crushed		strong limonite + Mn	158-162.5' fault with limonitic gouge, limonite and Mn + other black coating on crushed surfaces.
160			~~~~~			
			crushed		Tr malachite	
	100		~~~~~ 20 cm			
			Becomes more massive	moderate silicification moderate sericite	weak-mod. limonite	
170					minor black coating on fractures	Limonite + Mn + ?? on fracture surfaces
	100		moderate fractures			
—						
180			fractures		Tr Cp	
		Medium to Fine QM	fairly massive	moderate sericite weak silic?		Sparse v. fine veins
	100				Tr Py, Ga	
			45°?			
—			~~~~~	sericite		
190			crushed, minor gouge		weak limonite	Crushed zone. Sericitic with no limonite at top, some limonite at bottom.
	95		~~~~~			

			small			
		Medium QM	~~~~~			15 cm gouge – limonitic
200						
	95			weak silicn		
			± massive			
				Tr Py		Few narrow pyrite veins.
206' E.O.H.						

DDH-03-5

Collar: L32E 580S, inclined -50° south

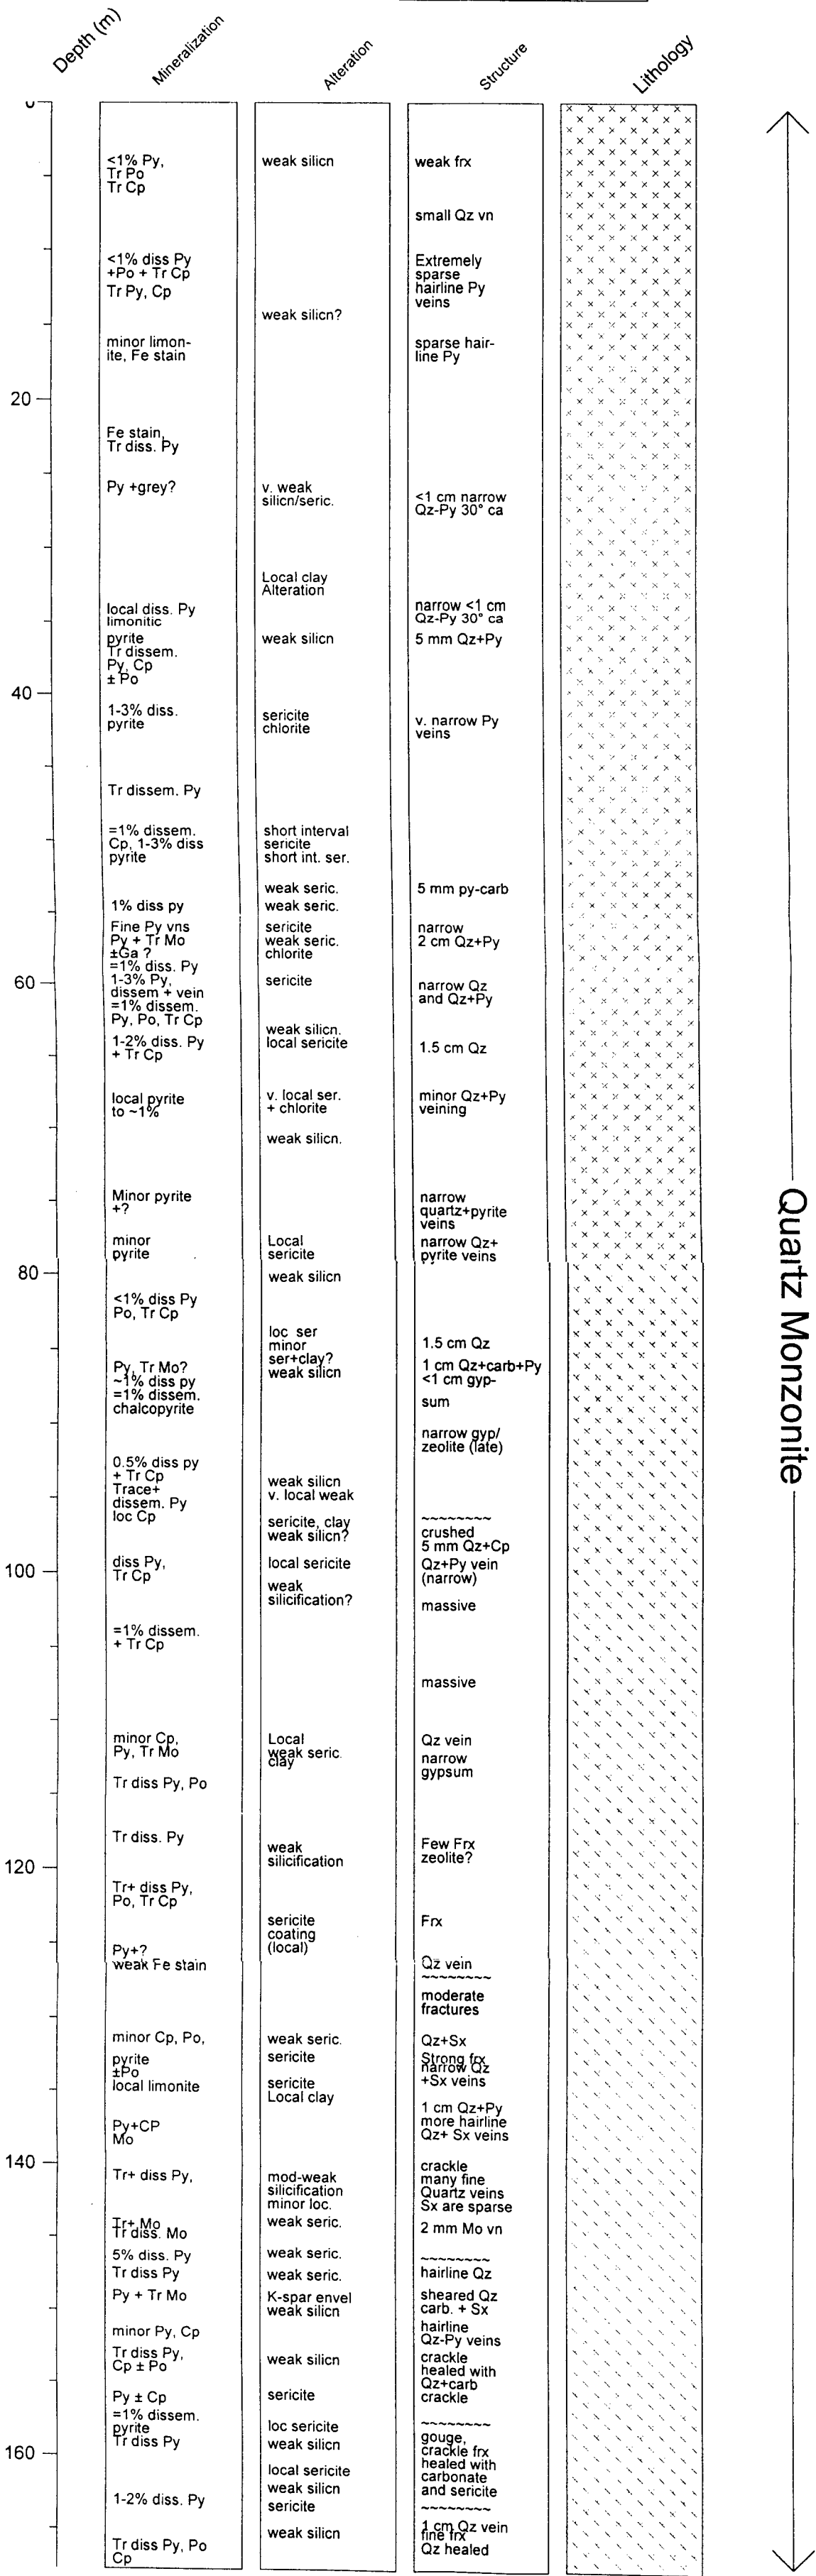

DDH-03-5		Grid Capital Corporation		AMI Project		09/04/03	
			Collar: L32E 580S -50° south	UTM 07V 523086E 7086431N	Dip tests: 550° 48°		Logged by B.K. Northcote
							Hole started Sept 1 Proposed depth 200 m (656 ft) Completed Sept 4 550 ft EOH
Depth (ft)	Recovery (%)	Samples	Lithology	Structure	Alteration	Mineralization	Remarks
							0-10' casing
10	—		Medium QM (bt±hb)	weak frx	weak silicn	<1% Py, Tr Po Tr Cp	Iron staining on fracture surfaces
		92					
20	—						
				small Qz vn <1 cm 15° ca			Vein limonitic
		96					
30	—						
				Extremely sparse hairline Py veins		<1% diss Py +Po + Tr Cp	
		93					
40	—		Medium QM			Tr Py, Cp	
		100			weak silicn?		
50	—						
				sparse hair- line Py		minor limon- ite, Fe stain	Staining on fracture surfaces
		98					
60	—						
			Weakly por- phyritic, with				

	97	K-spar pheno-crysts				
70	—				Fe stain, Tr diss. Py	Some limonite, Fe stain on fracture surfaces
	100					
80	—					
				v. weak silicn/seric.	Py +grey?	Possible fine Ga or Mo
	98	Medium QM	<1 cm narrow Qz-Py 30° ca			v. minor sericite associated with vein
90	—					
	98	weakly porphyritic				
100	—					
				Local clay Alteration		minor clay alteration associated with fractures
	100					
			narrow <1 cm Qz-Py 30° ca		local dissem. pyrite	
110	—				limonitic fractures	
	99					Some Fe staining on fracture surfaces
			5 mm Qz+Py 35° ca	weak silicn	pyrite Tr dissem. Py, Cp	
120	—					
	100	Medium QM weakly porph. or sub. porph.			Tr diss. Py ± Po	

130—						
				sericite	1-3% diss.	133.5-136' small zone of sericite and
	99		v. narrow Py	chlorite	pyrite	chlorite alteration associated with
			veins			narrow Qz-Py veins.
140—						
	91					
150—		Becomes			Tr dissem. Py	
		slightly finer				
		grained,				
		phenocrysts				
	100	more conspic-				
		uous.				
160				short interval	□ 1% dissem.	Minor disseminated chalcopyrite
				sericite	Cp, 1-3% diss	
				short int. ser.	pyrite	
	100					
170						
			5 mm py-carb	weak seric.		
			vein 20°			Very local weak sericite
	100					
				weak seric.	1% diss py	175' one foot interval of sericite
						alteration with fine disseminated
						chalcopyrite.
—179.5						
180						
		Medium QM	narrow	sericite	Fine Py vns	A few small stringers together
			Qz+Py			
	100		2 cm Qz+Py	weak seric.	Py + Tr Mo	Vein contains coarse pyrite, grey
			25° ca	chlorite	±Ga ?	quartz.
190—					□ 1% dissem.	
					pyrite	
	96		narrow Qz	sericite	1-3% Py,	
					dissem + vein	

			and Qz+Py			
200	—		Coarsening again	sericite	□ 1% dissem. Py, Po, Tr Cp	
	98			weak silicn.	1-2% diss. Py + Tr Cp	
210	—		1.5 cm Qz 45° ca	local sericite	minor Py in a vein, Tr diss pyrite	
	100					
220	—		minor Qz+Py veining	v. local ser. + chlorite	local pyrite to ~1%	
			Some growth- zoned K-spar phenocrysts to 2 cm (sparse)			
	100					
230	—			weak silicn.		
	100					
240	—					
			narrow quartz+pyrite veins	Local sericite	Minor pyrite +?	Greyish quartz
	100					
250	—					
			narrow Qz+ pyrite veins	Local sericite	minor pyrite	Frequency of narrow (<7 mm) veins picks up slightly. 4-5 in the core box.
	96					
260	—		Medium QM	weak silicn		

	100				<1% diss Py Po, Tr Cp	
270	—					
				loc ser minor		
	100		1.5 cm Qz	ser+clay?		Coarse quartz vein in short bleached interval.
280	—		1 cm Qz+carb +py 15°		Py, Tr Mo?	Vein at 180.5
				weak silicn	~1% diss py	
			<1 cm gyp- sum, high angle		□1% dissem. chalcopryrite	Some disseminated chalcopryrite near vein
	100					Drusy gypsum in vein is probably a late fracture coating.
290	—				Trace disseminated pyrite	
	100		narrow gyp/ zeolite (late)			
				weak silicn		
300	—					
			Weakly por- phyritic, med- ium grained		0.5% diss py + Tr Cp	
	100			weak silicn v. local weak sericite	Trace+ dissem. Py loc Cp	
310	—					
			30 cm ~~~~~ crushed	Local clay	weak Fe stain	
	99			weak silicn?		
320	—		5 mm Qz+Cp vein 20°		Cp, assoc. dissem. Py, Cp	Chalcopryrite vein at 321.3' – irregular
	100		Qz+Py vein (narrow)	local sericite	Pyrite, Tr+ diss Py, Tr Cp	

330	—			weak silicification?		
			massive			
	100					
340	—				□ 1% disse. + Tr Cp	
	100					
350	—		massive			
	96					
360	—					
			Qz vein, 1.5 cm, 25°	Local sericite	minor Cp, Py, Tr Mo	363'
	100			weak seric.	Tr+ diss Py, Po, Tr Cp	
			narrow gypsum vein (low angle)	clay		2' bleached interval associated with low angle gypsum vein 368-370'
370	—					
					Tr diss Py, Po	
	100					Minor zeolite ± carbonate in fractures
380	—					
	99				Tr diss. Py	
			Few Frx (zeolite? coating)	weak silicification		
390	—	Medium QM sub porph				

	100						
						Tr+ diss Py, Po, Tr Cp	
400	—						Narrow gypsum vein
				Frx	sericite		
				low	coating		More gypsum veinlets
	100			angle	(local)		
410	—					Py+? weak Fe stain	Quartz vein with a dark centre + pyrite 413' at top of shear zone
				Qz vein, 2 cm, 40°			
				~~~~~			
	79			gouge, crushed			
				~~~~~			
				moderate			
420	—			fractures			
	98						
				broken Qz + Sx vein	weak seric.	minor Cp, Po, Bo?, Py	
430	—						
				Strong frx	sericite		
						pyrite ±Po	
	97			A few very narrow Qz +Sx veins			
					sericite		
440	—			Strong frx	Local clay	local limonite	
				1 cm Qz+Py			
	92						
				more hairline Qz+ Sx veins			
				eg 45°		Py+CP Mo	
450	—						Mo in a sheared Quartz + Sx vein
	100			Medium QM sub porph			
				crackle			

460—			many fine Quartz veins Sx are sparse	mod-weak silicification minor loc. sericite	Tr+ diss Py,	
93						
470—			2 mm Mo vn 45° ca	weak seric. (local) moderate sericite (loc)	Tr+ Mo Tr diss. Mo	Narrow molybdenite vein 471.5'
100						
			30 cm ~~~~~	weak seric. strong seric.	5% diss. Py	Short interval of disseminated pyrite in a sericitic crushed zone.
480—			gouge,			
			many hairline Qz carb. veins	weak seric. +silicn	Tr diss Py	
99			sheared Qz carb. + Sx vein ~8°	K-spar envel	Py + Tr Mo +	Minor disseminated Mo in wall rock vein is a few mm wide, stretched.
490—				weak silicn	Tr dissPy	
			narrow + hairline Qz-Py veins		Tr Cp minor Py, Cp in veins	All < 1 cm, 25-50° ca. One has sheared, ground sulfide and carbonate.
100						
500—		Medium QM with sparse K-spar pheno crysts.	crackle healed with Qz+carb	weak silicn	Tr diss Py, Cp ± Po	
96						Some large 2 cm phenocrysts with growth zones.
510—			crackle healed mainly with sericite	sericite	Py ± Cp	A quartz + pyrite vein to ~1 cm.
				loc sericite		
100			~5 cm ~~~~~ gouge, crackle frx healed with		□1% dissem. pyrite	Locally Sericitic and black gouge.
520—			carbonate and sericite	weak silicn	Tr diss Py	
99						

					local sericite		
530	—				weak silicn		
						1-2% diss. Py	
				10 cm			
	97			~~~~~	sericite		
		Medium QM		gouge 45°			
				1 cm Qz vein			
540	—			fine frx	weak silicn		
				healed			
				with			
				quartz		Tr diss Py, Po	Hairline Po + Cp veinlet.
						Cp	
	100						
						Tr diss Py, Po	
550	E.O.H.					Cp	

APPENDIX B: ANALYTICAL RESULTS

From ACME ANALYTICAL LABORATORIES LTD. 852 E. HASTINGS ST. VANCOUVER BC V6A 1R6
To Grid Capital Corporation PROJECT AM1
Acme file # A304857 Page 1 Received: OCT 7 2003 * 84 samples in this disk file.
Analysis: GROUP 1DX - 15.0 GM

		Interval		ELEMENT Mo		Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	U	Au	Th	Sr	Cd	Sb	Bi	Al	Na	K	W	Hg	Sc	Ti	S	Ga	V	Ca	P	La	Cr	Mg	Ba	Ti	B	Se	Sample		
DDH	From	To	Ft	Meters	SI	SAMPLES	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppb	ppm	ppm	ppm	ppm	ppm	%	%	%	ppm	ppm	ppm	ppm	%	ppm	ppm	%	%	ppm	ppm	%	%	ppm	ppm	ppm	gm		
03-01	35.5	39.0	3.5	1.07	C 157201	5.9	72.1	14.7	19	0.2	2.9	4.4	161	0.04 < .5	< .1	2 < .1	18.4	31	0.2	0.3	1.6	0.01	0.434 < .01	0.17	0.1 < .01	< .1	< .1	0.06 < 1	< 1	0.08 < .001	< 1	2	1.9 < .01	2	0.001	2	< .5	0					
	323.5	326.8	3.3	1.01	C 157202	1.5	95.4	9	27	0.1	3.9	3.8	448	1.63	5.3	24.6	5.3	37	0.2	0.3	3.9	0.67	0.084	0.23	1.3 < .01	1.4	0.2	0.31	4	25	0.24	0.045	23	9.7	0.29	129	0.089	6	< .5	2000			
	425.5	428.8	3.3	1.01	C 157203	4.3	115.4	13.5	17	0.6	3.9	5	157	2.48	4.1	8.9	9.7	46 < .1	0.3	0.3	0.8	0.88	0.042	0.23	0.7 < .01	2	0.3	0.38	4	31	0.82	0.072	30	8.7	0.42	101	0.094	6		0.7	1900		
	575.5	576.7	1.2	0.37	C 157204	4	16.1	7.8	24	0.1	1.4	6.9	365	1.71	7.5	12.7	4.4	18.3	37	0.1	0.3	9.9	0.57	0.059	0.18	1.8	0.01	1.2	0.2	0.58	3	20	0.48	0.033	17	9.8	0.22	101	0.062	5		0.7	1500
	592.0	595.5	3.5	1.10	C 157205	5.9	47.6	15.2	33	0.1	2.3	3.7	410	1.94 < .5		25.2	3.3	20.3	35	0.1	0.2	3.8	0.72	0.03	0.14	1.4 < .01	2	0.1	0.28	3	32	1.09	0.091	38	6.2	0.25	62	0.043	5		0.6	1200	
03-02	58.0	63.0	5.0	1.52	C 157206	35	1167.3	12.9	215	0.5	30.1	41.8	1405	2.31	2.5	7	3.7	22.3	68	0.2	0.2	0.7	0.89	0.049	0.16	1.2	0.01	1.9	0.2	0.32	4	37	1.1	0.074	34	7.2	0.3	98	0.073	9	< .5	2300	
	63.0	68.0	5.0	1.52	C 157207	51.2	508.7	8.5	134	0.4	22.7	33.6	2386	3.1	5.5	3.8	2.1	19	86	3.6	0.6	2.6	2.71	0.017	0.42	0.6	0.02	3.9	0.4	0.65	9	49	0.81	0.083	93	25.7	0.96	222	0.078	3		2.5	600
	68.0	72.3	4.3	1.31	C 157208	132.4	370.5	21.5	334	0.5	13.8	16.4	1552	3.02	1.9	2.9	1.3	18.2	58	9.3	0.3	2.11	0.02	0.4	0.5 < .01	3.9	0.3	0.71	8	48	0.69	0.084	37	26.8	1	241	0.091	3		2	500		
	76.0	79.3	3.3	1.01	C 157209	56.1	210.2	13.5	469	0.3	8	19.8	1862	2.05	20.2	4.8	1.9	22.6	42	3.9	2.5	0.9	1.31	0.009	0.28	2.1	0.01	2.8	0.3 < .05	5	22	0.33	0.076	61	18.9	0.25	194	0.012	5		0.7	2100	
	86.0	89.3	3.3	1.01	C 157210	62	105.6	7.3	230	0.2	3.1	7.2	2181	2.76	70.6	4.9	3.8	22.4	101	5.8	1.4	0.6	1.74	0.011	0.16	0.6	0.02	2.7	0.2 < .05	6	30	0.46	0.072	37	13.6	0.48	219	0.017	3		0.7	2000	
	92.7	96.0	3.3	1.01	C 157211	72.7	50.3	27.4	324	0.2	3.5	9.9	1717	2.01	49.6	5.1	2.4	17.1	1625	3.2	2.2	2.3	1.54	0.038	0.24	0.5 < .01	2.1	0.3 < .05	5	29	0.53	0.075	41	6.6	0.35	1230	0.044	4	< .5	1500			
	101.5	104.7	3.2	0.98	C 157212	19.1	84.1	15.8	301	0.1	2.2	8.1	747	2.45	90.3	4	2.9	18	1174	3.9	1.9	0.8	1.81	0.028	0.28	0.8	0.01	2.1	0.4 < .05	7	26	0.56	0.073	45	7.3	0.34	797	0.03	6	< .5	2300		
	104.7	107.9	3.2	0.98	C 157213	24.3	100.1	17.4	349	0.1	3.3	9.1	1031	1.97	90.5	3.4	5.3	17.1	381	3.5	1.5	0.6	1.71	0.041	0.19	0.4 < .01	2	0.2 < .05	5	27	0.63	0.072	34	6.5	0.33	294	0.017	5	< .5	2000			
	117.0	120.2	3.2	0.98	C 157214	72.3	660	5068.9	596	8.9	4.4	20.4	789	2.14	80.6	3.4	1.8	16.7	149	5.3	1.5	0.6	1.36	0.038	0.23	0.9 < .01	2.2	0.3 < .05	5	30	0.44	0.078	39	8.5	0.33	199	0.044	4	< .5	2100			
	146.0	149.3	3.3	1.01	C 157215	187.9	170.4	208.7	276	3.5	121.1	12.4	805	3.1	1210.5	7.4	126.9	16.9	15	9.3	56.2	5	0.88	0.012	0.35	20.8	0.06	1.2	0.4	1.99	2	10	0.53	0.073	29	5	0.08	59	0.005	9	1.8	2400	
	155.6	159.0	3.4	1.04	C 157216	74.8	143	55.9	152	0.1	2.7	11.5	809	2.72	136.8	7.8	24.7	15.1	59	2.2	2.5	8.6	1.87	0.011	0.2	2.4	0.01	2	0.3	1.32	7	21	0.58	0.073	47	199.1	0.45	70	0.002	3	0.8	2000	
	161.0	164.4	3.3	1.01	C 157217	16.7	65.3	25.2	206	0.8	2.9	28.3	578	2.2	10.7	7.3	6.7	16.4	35	2.7	1.2	0.5	1.08	0.022	0.22	0.5	0.01	1.6	0.2	1.07	3	17	1.24	0.068	36	4.5	0.23	70	0.008	5	1	1900	
	1/2 sample	0.0	18.0	18.0	5.49	C 157218	59.9	341.9	7.2	185	0.2	5.7	12.3	543	3.49	57.9	5.4	8.6	14.8	37	1.2	1	31.4	1.37	0.023	0.21	1 < .01	1.8	0.3	1.98	4	20	0.89	0.067	35	6.2	0.25	64	0.012	2	2.2	1700	
	1/2 sample	18.0	28.0	10.0	3.05	C 157219	29.6	421.7	8.8	182	0.3	10.1	12.7	486	1.61	4.4	8.7	3	23	28	1.6	0.6	0.6	1	0.024	0.29	0.6 < .01	2	0.3 < .05	4	11	0.21	0.068	40	7.6	0.31	148	0.008	3	0.5	900		
		18.0	28.0	10.0	3.05	C 157220	130.4	382.2	10.5	149	0.4	11.4	16.1	1342	1.88	1	5.5	2	22.9	21	1.5	0.3	0.7	1.1	0.026	0.26	0.3	0.13	4	19	0.18	0.072	26	12.3	0.29	380	0.005	4	1.7	1100			
					RE C 1572	134.6	392.2	9.9	154	0.4	12.3	16.8	1378	1.67	2.3	5.2	2.8	24	72	1.9	0.5	0.7	1.12	0.026	0.3	0.6 < .01	2.6	0.3	0.16	4	24	0.24	0.078	28	14	0.44	883	0.039	4	1.4	1300		
					RRE C 157	131.4	376.5	10.1	145	0.4	12	15.2	1236	1.7	2.6	5.7	2.2	23.7	73	2	0.5	0.8	1.17	0.026	0.3	0.6 < .01	2.7	0.3	0.14	4	25	0.25	0.078	28	15.2	0.45	885	0.042	5	1.4	0		
	28.0	34.0	6.0	1.83	C 157221	35.9	691.1	5.3	316	0.3	17.9	18.2	1130	1.73	2.6	5.5	7.3	23	73	2	0.5	1	1.15	0.03	0.32	0.9 < .01	2.8	0.3	0.18	5													

DDH	Interval		From	To	Ft	Meters	ELEMENT SAMPLES	Mo ppm	Cu ppm	Pb ppm	Zn ppm	Ag ppm	Ni ppm	Co ppm	Mn ppm	Fe %	As ppm	U ppm	Au ppb	Th ppm	Sr ppm	Cd ppm	Sb ppm	Bi ppm	Al %	Na %	K %	W ppm	Hg ppm	Sc ppm	Ti ppm	S %	Ga ppm	V ppm	Ca %	P %	La ppm	Cr ppm	Mg %	Ba ppm	Ti %	B ppm	Se ppm	Sample gm
03-02	142.9	146.0	3.1	0.95	C 157244	266.9	65.1	7.3	175	0.1	3.8	6.2	657	1.43	18.4	6.6	0.9	218	0.3	1.5	0.5	1.4	0.026	0.2	1.1 < .01	2.1	0.2	0.27	4	20	0.6	0.072	59	6.7	0.28	200	0.019	3	< .5		2100			
	149.3	152.5	3.2	0.98	C 157245	91.6	117.6	16.7	63	0.2	1.5	12.1	805	1.86	26.6	9.2	5.2	132	0.2	2.7	1.03	0.029	0.22	0.7	0.01	2.1	0.3	1.05	3	20	1.15	0.071	35	5.4	0.27	125	0.025	2		0.7	2800			
	152.5	155.6	3.1	0.95	C 157246	4	70.5	22	135	0.3	1.9	7.3	944	1.81	39	7.7	3.8	29	1.9	1.5	0.9	0.77	0.016	0.23	0.6 < .01	1.3	0.3	0.84	3	9	1.11	0.065	32	5.1	0.18	58	0.008	6		0.5	1800			
	163.4	167.3	3.9	1.19	C 157247	21.8	68.3	8.3	20	0.1	1.5	5.1	630	1.54	1.7	10.3	0.5	23.9	103	0.1	0.3	1.9	0.82	0.032	0.16	1	0.01	2.2	0.2	0.24	3	24	1.14	0.058	34	5	0.3	102	0.024 < 1		0.6	2500		
	167.3	170.6	3.3	1.01	C 157248	11	91	11.3	121	0.1	4.4	6	630	1.81	25	10.1	2.1	27.4	149	1.1	0.8	2.2	1.32	0.017	0.17	1.3	0.01	2.5	0.2	0.52	4	21	0.78	0.051	32	10.5	0.37	94	0.011	3	< .5		1800	
	170.6	173.9	3.3	1.01	C 157249	19.6	85.5	7.5	52	0.1	2.1	4.3	496	1.79	4.7	12.8 < .5		27.6	174	0.3	0.3	2.2	0.96	0.033	0.23	0.8	0.01	2.6	0.2	0.4	4	33	0.8	0.047	24	7	0.37	130	0.059	2	< .5		1900	
	173.9	177.2	3.3	1.01	C 157250	20.7	145.9	43.7	111	0.6	2.6	12.4	792	2	1026.4	10.7	52	21	234	0.8	1.7	2.2	1.43	0.022	0.22	0.9	0.01	2.2	0.3	0.9	5	22	1.53	0.06	29	7.4	0.3	140	0.02	6	< .5		1600	
					RE C 1572	20.1	141.7	44	112	0.5	1.8	12.3	782	1.99	1032	10.2	49.8	20.6	222	0.7	1.8	2.1	1.4	0.022	0.22	0.8	0.01	2.1	0.3	0.92	4	22	1.52	0.058	27	7.5	0.3	135	0.02	3		0.6	0	
					RRE C 157	16.4	137.8	48.8	139	0.6	1.9	13.4	845	2.14	1253.5	11.8	64.8	23.7	232	0.9	2.2	1.9	1.45	0.024	0.23	0.6	0.01	2.3	0.3	1.03	4	24	1.67	0.062	29	6.5	0.32	140	0.023	1		0.6	0	
	177.2	180.5	3.3	1.01	C 157251	56.5	92.6	9.5	63	0.1	2.3	6.4	628	1.71	10.5	12.5	0.7	20.9	171	0.2	0.6	1.4	0.026	0.21	1.1 < .01	2.1	0.2	0.53	4	18	1.23	0.06	35	6.4	0.28	108	0.017	1	< .5		1700			
	180.5	183.8	3.3	1.01	C 157252	7	81.5	10.6	231	0.1	2.3	5.3	548	1.74	12.1	8.8 < .5		18.5	208	1.3	0.7	1.5	0.035	0.17	0.3	0.01	2.3	0.2	0.14	5	26	0.98	0.067	44	6	0.37	135	0.02	1	< .5		2000		
	183.8	187.1	3.2	0.98	C 157253	27.8	16.1	6.5	51 < .1		1.6	4.3	459	1.58	4.9	14.2	2	18.7	544	0.1	0.3	0.3	1.17	0.036	0.19	0.6	0.01	2.1	0.2	0.15	4	27	0.88	0.057	34	6.8	0.33	267	0.032	1	< .5		2100	
	195.6	198.4	2.8	0.85	C 157254	10.4	53.6	7.8	36	0.1	2.3	6.1	570	1.71	9.7	8.2 < .5		28	956	0.1	0.6	2.3	0.022	0.2	0.8 < .01	2.3	0.3	0.39	6	27	1.56	0.053	28	6.4	0.46	360	0.016 < 1		< .5		1900			
	198.9	202.2	3.3	1.01	C 157255	216.4	84.2	7.6	79	0.1	3.2	7.2	585	1.26	5.7	18.1	0.8	20.1	96	0.2	0.4	1.1	0.96	0.016	0.14	1.1 < .01	1.4	0.2	0.67	3	13	1.89	0.059	51	7.3	0.18	40	0.01	2		0.5	2000		
	454.0	456.8	2.8	0.85	C 157256	773.7	10.7	34.9	11	0.1	0.3	3.6	842	2.17	7	27.1	3.2	14.6	50 < .1		0.2	0.4	0.4	0.015	0.16	0.8 < .01	0.9	0.2	1.83	2	4	1.9	0.046	23	2.8	0.11	45 < .001		0.8	1500				
	459.1	461.8	2.7	0.82	C 157257	428.3	169.1	8.2	29	0.1	14.2	9.5	670	2.21	14.3	13.2	1.7	17.4	125 < .1		0.3	0.5	1.6	0.02	0.36	0.9	0.02	4.4	0.4	0.74	7	43	1.18	0.067	83	21.4	0.78	80	0.038 < 1		0.8	1600		
	462.5	465.0	2.5	0.76	C 157258	375.8	9.9	19.3	16	0.1	0.7	2.1	524	2.18	7.3	17.4	2	17.2	68 < .1		0.2	0.4	0.55	0.024	0.16	0.6 < .01	1.3	0.1	1.46	2	13	1.12	0.049	29	4.5	0.21	73	0.01	1	< .5		1800		
	494.4	496.3	1.9	0.58	C 157259	35.2	31.6	9	23	0.1	1.8	2.7	946	1.22	6.7	8.2 < .5		16.9	78	0.1	0.4	1.1	0.64	0.023	0.14	11.3	0.01	1.5	0.2	0.18	3	13	1.62	0.053	25	6.2	0.24	58	0.002	4	< .5		1200	
	545.0	548.0	3.0	0.91	C 157260	6.7	148.9	1612.6	445	2.7	0.9	2.7	377	1.91	1684.1	6.8	35.9	19.7	338	4.1	1.8	1	0.64	0.031	0.16	0.7	0.01	1.3	0.2	1.02	3	15	0.85	0.051	17	5.5	0.26	139	0.01 < 1		< .5		2300	
	552.5	554.7	2.2	0.67	C 157261	2	153.6	864.3	23	2.7	2.1	5	505	1.7	38.3	7.8	5.7	17.6	66	0.2	0.8	9.5	0.66	0.018	0.16	2.9 < .01	1.1	0.2	1.21	2	5	1.06	0.049	23	5.3	0.18	55	0.004	2	< .5		1400		
	563.7	565.5	1.8	0.55	C 157262	1.7	24.1	56.4	38	0.3	1.2	1.6	850	1.46	21.2	6.9	3.4	17.4	96	0.2	0.4	0.7	0.65	0.032	0.17	0.8	0.01	1.7	0.2	0.13	3	17	1.3	0.059	21	5.3	0.22	186	0.016 < 1		< .5		1200	
	568.0	569.9	1.9	0.58	C 157263	4.8	229.6	632	76	12.9	2.2	12.9	1016	2.76	1768.7	4.3	59.8	17.2	74	0.8	4.4	43.5	0.69	0.013	0.21	1.1	0.02	1.2	0.3	2.09	2	6	1.6	0.054	23	5.3	0.17	56	0.01	3		0.7	1400	
	614.5	617.4	2.9	0.88	C 157264	7	76	1119.6	301	7.6	0.7	4.5	2423	2.28	1159.7	6.8	20.9	16.8	88	3.1	9.6	15.8	0.66	0.012	0.17	0.7	0.02	1.4	0.2	0.89	2	5	2.58	0.059	22	3.2	0.13	107	0.004	5	< .5		2300	
	592.0	595.0	3.0	0.91	C 157265	3	102.9	1266.7	431	11.7	1.1	13.5	1085	2.01	234.4	5.2	10.6	18.2	150	3.8	0.9	71.7	0.79	0.014	0.18																			

From ACME ANALYTICAL LABORATORIES LTD. 852 E. HASTINGS ST. VANCOUVER BC V6A 1R6
To Grid Capital Corporation PROJECT AM1

Acme file # A304858 Page 1 Received: OCT 7 2003 * 46 samples in this disk file.

DDH	From	To	Interval		SI	ELEMENT Au**	Sample gm
			Ft	Meters		SAMPLES ppb	
						< 2	0
03-03	41.0	44.3	3.3	1.01	C 157276	5	1700
	44.3	47.0	2.7	0.82	C 157277	4	1700
	61.7	65.0	3.3	1.01	C 157278	5	1500
	65.0	68.3	3.3	1.01	C 157279	5	2100
	68.3	71.0	2.7	0.82	C 157280	7	1900
	155.0	158.3	3.3	1.01	C 157281	< 2	2500
	158.3	161.3	3.0	0.91	C 157282	4	2400
	161.3	164.9	3.6	1.10	C 157283	3	2500
	165.0	168.2	3.2	0.98	C 157284	2	2500
	168.2	171.5	3.3	1.01	C 157285	2	2300
	171.5	176.4	4.9	1.49	C 157286	3	3500
	176.4	181.3	4.9	1.49	C 157287	< 2	3600
	186.2	189.5	3.3	1.01	C 157288	6	2200
	189.5	192.5	3.0	0.91	C 157289	3	2900
	199.5	204.4	4.9	1.49	C 157290	6	3100
					RE C 1572	8	0
					RRE C 157	4	0
	204.4	209.3	4.9	1.49	C 157291	5	3400
	209.3	214.2	4.9	1.49	C 157292	4	3500
	214.2	219.1	4.9	1.49	C 157293	3	3700
	219.1	224.0	4.9	1.49	C 157294	5	3300
	224.0	228.9	4.9	1.49	C 157295	2	4000
	228.9	233.8	4.9	1.49	C 157296	3	3900
	233.8	238.7	4.9	1.49	C 157297	12	3800
	238.7	243.6	4.9	1.49	C 157298	7	3500
	243.6	248.5	4.9	1.49	C 157299	4	3700
	248.5	253.4	4.9	1.49	C 157300	4	3300
	253.4	258.3	4.9	1.49	C 157301	6	3800
	258.3	263.2	4.9	1.49	C 157302	3	4200
	263.2	268.1	4.9	1.49	C 157303	3	3600
	268.1	273.0	4.9	1.49	C 157304	6	3800
	273.0	277.9	4.9	1.49	C 157305	3	4000
	277.9	282.8	4.9	1.49	C 157306	7	3500
	282.8	287.7	4.9	1.49	C 157307	5	3000
	287.7	292.6	4.9	1.49	C 157308	6	3700
					STANDAR	492	0
	292.6	297.5	4.9	1.49	C 157309	9	3500
	297.5	299.5	2.0	0.61	C 157310	4	1700
	339.9	344.8	4.9	1.49	C 157311	8	2800
	344.8	349.7	4.9	1.49	C 157312	2	3300
	349.7	354.6	4.9	1.49	C 157313	2	3900
	430.0	434.9	4.9	1.49	C 157314	7	3800
	434.9	439.8	4.9	1.49	C 157315	2	3600
	415.0	416.8	1.8	0.55	C 157316	5	1000
	445.0	446.7	1.7	0.52	C 157317	3	1200
					STANDAR	495	0

From ACME ANALYTICAL LABORATORIES LTD.

To Grid Capital Corporation PROJECT AM1

Acme file # A304859 Received: OCT 7 2003 • 5 samples in this disk file.

Analysis: GROUP 7AR - 1.000 GM

DDH	From	To	Interval Ft	Meters	SI	ELEMENT Pb SAMPLES %	Ag** gm/mt	Au** gm/mt	Sample gm
						< .01	< .3	< .01	0
03-04	120.8	122.4	1.6	0.49	C 157320	1.94	64.5	0.23	1000
	122.4	122.9	0.5	0.15	C 157321	62.34	3099.4	1.38	1200
	122.9	124.5	1.6	0.49	C 157322	9.5	1770	1.05	1000
					STANDAR	1.48	152.5	3.3	0

APPENDIX C: CERTIFICATES OF ANALYSIS



GEOCHEMICAL ANALYSIS CERTIFICATE

Grid Capital Corporation PROJECT AM1 File # A304857 Page 1
1075 Duchess Ave, West Vancouver BC V7T 1G8 Submitted by: Leo King

SAMPLE#	Mo ppm	Cu ppm	Pb ppm	Zn ppm	Ag ppm	Ni ppm	Co ppm	Mn ppm	Fe %	As ppm	U ppm	Au ppb	Th ppm	Sr ppm	Cd ppm	Sb ppm	Bi ppm	V ppm	Ca %	P %	La ppm	Cr ppm	Mg %	Ba ppm	Ti %	B %	Al %	Na %	K %	W ppm	Hg ppm	Sc ppm	Tl ppm	S %	Ga ppm	Se ppm	Sample gm
SI	.1	.8	2.4	<1	.1	.6	<1	<1	.04	<.5	<.1	2.0	<.1	2	<.1	.1	1.6	<.1	.08	<.001	<.1	1.9	<.01	2	.001	2	.01	.434	<.01	.1	<.01	<.1	<.1	.06	<.1	<.5	-
C 157201	5.9	72.1	14.7	19	.2	2.9	4.4	161	1.63	5.3	24.6	5.3	18.4	31	.2	.3	3.9	25	.24	.045	23	9.7	.29	129	.089	6	.67	.084	.17	1.3	<.01	1.4	.2	.31	4	<.5	2000
C 157202	1.5	95.4	9.0	27	.1	3.9	3.8	448	2.48	4.1	8.9	9.7	17.3	46	<.1	.3	.8	31	.82	.072	30	8.7	.42	101	.094	6	.88	.042	.23	.7	<.01	2.0	.3	.38	4	.7	1900
C 157203	4.3	115.4	13.5	17	.6	3.9	5.0	157	1.71	7.5	12.7	4.4	18.3	37	.1	.3	9.9	20	.48	.033	17	9.8	.22	101	.062	5	.57	.059	.18	1.8	.01	1.2	.2	.58	3	.7	1500
C 157204	4.0	16.1	7.8	24	.1	1.4	6.9	365	1.94	<.5	25.2	3.3	20.3	35	.1	.2	3.8	32	1.09	.091	38	6.2	.25	62	.043	5	.72	.030	.14	1.4	<.01	2.0	.1	.28	3	.6	1200
C 157205	5.9	47.6	15.2	33	.1	2.3	3.7	410	2.31	2.5	7.0	3.7	22.3	68	.2	.2	.7	37	1.10	.074	34	7.2	.30	98	.073	9	.89	.049	.16	1.2	.01	1.9	.2	.32	4	<.5	2300
C 157206	35.0	1167.3	12.9	215	.5	30.1	41.8	1405	3.10	5.5	3.8	2.1	19.0	86	3.6	.6	2.6	49	.81	.083	93	25.7	.96	222	.078	3	2.71	.017	.42	.6	.02	3.9	.4	.65	9	2.5	600
C 157207	51.2	508.7	8.5	134	.4	22.7	33.6	2386	3.02	1.9	2.9	1.3	18.2	58	9.3	.3	.3	48	.69	.084	37	26.8	1.00	241	.091	3	2.11	.020	.40	.5	<.01	3.9	.3	.71	8	2.0	500
C 157208	132.4	370.5	21.5	334	.5	13.8	16.4	1552	2.05	20.2	4.8	1.9	22.6	42	3.9	2.5	.9	22	.33	.076	61	18.9	.25	194	.012	5	1.31	.009	.28	2.1	.01	2.8	.3	<.05	5	.7	2100
C 157209	56.1	210.2	13.5	469	.3	8.0	19.8	1862	2.76	70.6	4.9	3.8	22.4	101	5.8	1.4	.6	30	.46	.072	37	13.6	.48	219	.017	3	1.74	.011	.16	.6	.02	2.7	.2	<.05	6	.7	2000
C 157210	62.0	105.6	7.3	230	.2	3.1	7.2	2181	2.01	49.6	5.1	2.4	17.1	1625	3.2	2.2	2.3	29	.53	.075	41	6.6	.35	1230	.044	4	1.54	.038	.24	.5	<.01	2.1	.3	<.05	5	<.5	1500
C 157211	72.7	50.3	27.4	324	.2	3.5	9.9	1717	2.45	90.3	4.0	2.9	18.0	1174	3.9	1.9	.8	26	.56	.073	45	7.3	.34	797	.030	6	1.81	.028	.28	.8	.01	2.1	.4	<.05	7	<.5	2300
C 157212	19.1	84.1	15.8	301	.1	2.2	8.1	747	1.97	90.5	3.4	5.3	17.1	381	3.5	1.5	.6	27	.63	.072	34	6.5	.33	294	.017	5	1.71	.041	.19	.4	<.01	2.0	.2	<.05	5	<.5	2000
C 157213	24.3	100.1	17.4	349	.1	3.3	9.1	1031	2.14	80.6	3.4	1.8	16.7	149	5.3	1.5	.6	30	.44	.078	39	8.5	.33	199	.044	4	1.36	.038	.23	.9	<.01	2.2	.3	<.05	5	<.5	2100
C 157214	72.3	660.0	5068.9	596	8.9	4.4	20.4	789	3.10	1210.5	7.4	126.9	16.9	15	9.3	56.2	5.0	10	.53	.073	29	5.0	.08	59	.005	9	.88	.012	.35	20.8	.06	1.2	.4	1.99	2	1.8	2400
C 157215	187.9	170.4	208.7	276	3.5	121.1	12.4	805	2.72	136.8	7.8	24.7	15.1	59	2.2	2.5	8.6	21	.58	.073	47	199.1	.45	70	.002	3	1.87	.011	.20	2.4	.01	2.0	.3	1.32	7	.8	2000
C 157216	74.8	143.0	55.9	152	.1	2.7	11.5	809	2.20	10.7	7.3	6.7	16.4	35	2.7	1.2	.5	17	1.24	.068	36	4.5	.23	70	.008	5	1.08	.022	.22	.5	.01	1.6	.2	1.07	3	1.0	1900
C 157217	16.7	65.3	25.2	206	.8	2.9	28.3	578	3.49	57.9	5.4	8.6	14.8	37	1.2	1.0	31.4	20	.89	.067	35	6.2	.25	64	.012	2	1.37	.023	.21	1.0	<.01	1.8	.3	1.98	4	2.2	1700
C 157218	59.9	341.9	7.2	185	.2	5.7	12.3	543	1.61	4.4	8.7	3.0	23.0	28	1.6	.6	.6	11	.21	.068	40	7.6	.31	148	.008	3	1.00	.024	.29	.6	<.01	2.0	.3	<.05	4	.5	900
C 157219	29.6	421.7	8.8	182	.3	10.1	12.7	486	1.88	1.0	5.5	2.0	22.9	21	1.5	.3	.7	19	.18	.072	26	12.3	.29	380	.005	4	1.10	.026	.26	.3	.01	2.2	.3	.13	4	1.7	1100
C 157220	130.4	382.2	10.5	149	.4	11.4	16.1	1342	1.67	2.3	5.2	2.8	24.0	72	1.9	.5	.7	24	.24	.078	28	14.0	.44	883	.039	4	1.12	.026	.30	.6	<.01	2.6	.3	.16	4	1.4	1300
RE C 157220	134.6	392.2	9.9	154	.4	12.3	16.8	1378	1.70	2.6	5.7	2.2	23.7	73	2.0	.5	.8	25	.25	.078	28	15.2	.45	885	.042	5	1.17	.026	.30	.6	<.01	2.7	.3	.14	4	1.4	-
RRE C 157220	131.4	376.5	10.1	145	.4	12.0	15.2	1236	1.73	2.6	5.5	7.3	23.0	73	2.0	.5	1.0	26	.24	.077	27	16.9	.46	699	.041	4	1.15	.030	.32	.9	<.01	2.8	.3	.18	5	1.4	-
C 157221	35.9	691.1	5.3	316	.3	17.9	18.2	1130	1.69	.9	6.5	3.0	22.7	31	4.6	.4	1.0	13	.61	.072	46	9.0	.16	233	.002	6	.93	.025	.30	.4	.01	2.2	.4	.39	3	1.2	2500
C 157222	63.4	419.9	8.0	164	.2	6.9	5.5	261	1.90	1.7	7.2	3.0	23.4	51	1.9	.7	3.2	16	.17	.065	28	10.6	.16	172	.004	6	1.09	.030	.32	.8	<.01	2.0	.4	<.05	4	1.6	500
C 157223	82.8	271.8	8.2	128	.2	4.0	2.9	158	1.54	7.9	6.2	2.6	22.8	47	1.3	.5	3.8	8	.16	.062	52	6.7	.15	124	.004	6	.88	.016	.43	1.0	<.01	1.6	.5	<.05	4	.7	200
C 157224	104.3	372.1	6.0	179	.1	4.1	4.7	255	1.71	10.2	6.1	2.7	23.9	37	1.1	.5	.8	10	.19	.064	51	7.1	.19	114	.006	7	.96	.012	.34	.6	.02	2.0	.3	<.05	5	.9	200
C 157225	77.2	289.6	7.4	72	.5	5.1	3.6	210	2.53	8.3	7.0	3.9	19.9	112	.4	.5	1.3	43	.30	.089	27	20.9	.60	324	.070	5	2.01	.027	.41	.6	.01	3.7	.4	<.05	8	2.4	300
C 157226	268.0	489.0	10.0	116	.4	8.4	7.5	248	5.58	24.2	5.7	4.1	18.7	154	.3	1.0	.7	55	.29	.130	22	25.9	.69	1252	.095	3	2.14	.025	.40	.7	.01	4.5	.4	.10	9	8.2	500
C 157228	97.3	142.8	16.5	715	.1	13.0	10.1	927	2.68	11.5	5.4	1.5	25.1	140	3.3	1.3	.9	34	.40	.078	37	15.5	.25	215	.013	1	1.54	.018	.20	1.2	<.01	3.0	.2	<.05	7	.6	2400
C 157229	24.8	61.3	12.1	179	.1	2.4	14.2	635	2.14	20.7	2.7	2.0	14.5	1217	2.1	.7	.5	34	.53	.085	30	7.1	.40	1172	.045	2	1.64	.032	.22	.4	.01	2.4	.4	<.05	6	<.5	2100
C 157230	13.0	76.4	13.6	159	.1	3.2	6.1	760	1.99	14.2	3.2	3.5	15.4	481	2.1	.6	.2	37	.47	.084	32	7.1	.46	490	.079	1	1.22	.036	.17	.7	.01	2.4	.2	.07	5	<.5	2700
C 157231	12.6	39.3	12.9	210	.3	3.0	6.2	1353	2.19	22.9	3.1	5.3	18.5	1147	2.5	.8	.3	32	.51	.078	37	7.8	.40	839	.032	3	1.55	.037	.27	.6	.01	2.2	.3	.15	6	<.5	1700
C 157232	7.2	68.9	25.3	279	.2	3.2	4.8	1102	2.00	24.9	2.4	7.7	16.0	220	3.1	.5	.8	26	.39	.072	35	6.9	.39	242	.030	3	1.10	.035	.26	.8	.01	1.9	.3	.20	7	<.5	1400
C 157233	11.9	91.5	18.2	254	.1	2.9	4.5	442	2.00	61.7	3.5	4.3	18.2	41	2.5	1.0	.5	28	.31	.075	32	8.7	.33	105	.023	1	1.16	.038	.22	.7	.02	2.2	.2	<.05	5	<.5	1500
STANDARD DS5	12.3	134.0	23.6	131	.3	24.6	11.8	773	3.00	17.5	5.6	40.3	2.7	47	5.2	3.8	5.7	62	.77	.085	13	176.6	.67	137	.111	16	2.12	.035	.15	4.6	.17	3.4	1.1	<.05	6	4.8	-

GROUP 1DX - 15.0 GM SAMPLE LEACHED WITH 90 ML 2-2-2 HCL-HNO3-H2O AT 95 DEG. C FOR ONE HOUR, DILUTED TO 300 ML, ANALYSED BY ICP-MS.

UPPER LIMITS - AG, AU, HG, W = 100 PPM; MO, CO, CD, SB, BI, TH, U & B = 2,000 PPM; CU, PB, ZN, NI, MN, AS, V, LA, CR = 10,000 PPM.

- SAMPLE TYPE: CORE R150 60C Samples beginning 'RE' are Reruns and 'RRE' are Reject Reruns.

DATE RECEIVED: OCT 7 2003 DATE REPORT MAILED: Oct 23/2003 SIGNED BY: [Signature] D. TOYE, C. LEONG, J. WANG; CERTIFIED B.C. ASSAYERS

All results are considered the confidential property of the client. Acme assumes the liabilities for actual cost of the analysis only.

Data EA



SAMPLE#	Mo ppm	Cu ppm	Pb ppm	Zn ppm	Ag ppm	Ni ppm	Co ppm	Mn ppm	Fe %	As ppm	U ppm	Au ppb	Th ppm	Sr ppm	Cd ppm	Sb ppm	Bi ppm	V ppm	Ca %	P %	La ppm	Cr ppm	Mg %	Ba ppm	Ti %	B ppm	Al %	Na %	K %	W ppm	Hg ppm	Sc ppm	Tl ppm	S %	Ga ppm	Se ppm	Sample gm
C 157234	7.0	78.4	7.3	206	.1	2.7	5.7	328	1.96	16.6	2.2	<.5	14.9	70	1.9	.3	.9	35	.42	.081	27	6.8	.37	113	.038	3	.79	.043	.14	.8	.01	2.0	.1	.12	4	<.5	1900
C 157235	9.0	112.2	10.5	282	.2	2.6	7.5	652	1.87	46.3	3.0	1.6	13.2	235	3.5	.9	.7	27	.64	.074	28	5.5	.30	213	.025	3	.91	.033	.17	.6	.01	1.8	.1	.18	4	.5	1800
C 157236	12.0	168.1	105.1	337	.7	3.4	10.2	737	2.08	110.9	5.0	17.3	15.4	30	10.0	5.6	1.4	16	.59	.075	29	6.7	.14	96	.011	6	.63	.022	.27	.8	.02	1.7	.3	.85	3	.8	2000
C 157237	27.0	100.6	327.0	342	.3	2.7	5.4	376	2.05	47.8	2.6	5.5	17.0	28	2.8	2.5	.6	24	.46	.078	30	6.0	.24	99	.020	6	.71	.032	.21	.9	<.01	1.8	.2	.27	4	<.5	2200
C 157238	14.8	58.9	28.0	239	.4	2.7	9.7	1059	1.95	28.9	6.2	3.5	16.4	39	2.0	4.3	6.7	22	1.13	.078	34	6.6	.28	116	.018	5	.67	.031	.20	.9	.01	2.0	.2	.34	3	<.5	2100
C 157239	35.7	61.0	57.2	151	.4	2.3	11.9	524	2.35	18.1	5.1	.9	15.5	34	1.1	.6	1.2	28	.80	.079	27	5.8	.27	154	.040	4	.63	.039	.21	.9	<.01	1.9	.2	.85	3	.9	1900
C 157240	67.6	64.1	14.2	108	.1	3.3	6.5	464	1.92	7.6	6.1	2.0	16.5	55	.2	.3	.4	32	.84	.079	36	8.8	.32	156	.053	8	.73	.051	.23	1.3	.02	2.1	.2	.24	4	.5	2200
C 157241	80.1	44.5	16.7	181	.2	2.3	6.3	387	1.93	66.4	4.3	4.8	16.7	30	1.2	1.7	.8	27	.63	.076	53	7.2	.26	122	.043	2	.67	.036	.23	.7	.01	2.1	.2	.44	4	<.5	2600
C 157242	5.2	21.2	6.9	104	<.1	3.1	7.4	440	2.10	21.7	4.7	1.7	15.1	29	1.1	.5	1.2	28	.65	.077	32	8.2	.27	125	.046	2	.66	.045	.24	1.0	.02	2.0	.2	.60	3	<.5	2000
C 157243	17.5	166.2	9.8	102	.1	2.7	7.5	358	1.71	10.0	5.5	6.0	19.8	39	3.3	.8	.3	27	.64	.076	29	7.3	.32	108	.055	2	.77	.053	.21	.8	.02	2.2	.2	.42	4	<.5	2000
C 157244	266.9	65.1	7.3	175	.1	3.8	6.2	657	1.43	18.4	6.6	.9	17.2	218	.3	1.5	.5	20	.60	.072	59	6.7	.28	200	.019	3	1.40	.026	.20	1.1	<.01	2.1	.2	.27	4	<.5	2100
C 157245	91.6	117.6	16.7	63	.2	1.5	12.1	805	1.86	26.6	9.2	5.2	19.2	132	.2	1.0	2.7	20	1.15	.071	35	5.4	.27	125	.025	2	1.03	.029	.22	.7	.01	2.1	.3	1.05	3	.7	2800
C 157246	4.0	70.5	22.0	135	.3	1.9	7.3	944	1.81	39.0	7.7	3.8	17.9	29	1.9	1.5	.9	9	1.11	.065	32	5.1	.18	58	.008	6	.77	.016	.23	.6	<.01	1.3	.3	.84	3	.5	1800
C 157247	21.8	68.3	8.3	20	.1	1.5	5.1	630	1.54	1.7	10.3	.5	23.9	103	.1	.3	1.9	24	1.14	.058	34	5.0	.30	102	.024	<.1	.82	.032	.16	1.0	.01	2.2	.2	.24	3	.6	2500
C 157248	11.0	91.0	11.3	121	.1	4.4	6.0	630	1.81	25.0	10.1	2.1	27.4	149	1.1	.8	2.2	21	.78	.051	32	10.5	.37	94	.011	3	1.32	.017	.17	1.3	.01	2.5	.2	.52	4	<.5	1800
C 157249	19.6	85.5	7.5	52	.1	2.1	4.3	496	1.79	4.7	12.8	<.5	27.6	174	.3	.3	2.2	33	.80	.047	24	7.0	.37	130	.059	2	.96	.033	.23	.8	.01	2.6	.2	.40	4	<.5	1900
C 157250	20.7	145.9	43.7	111	.6	2.6	12.4	792	2.00	1026.4	10.7	52.0	21.0	234	.8	1.7	2.2	22	1.53	.060	29	7.4	.30	140	.020	6	1.43	.022	.22	.9	.01	2.2	.3	.90	5	<.5	1600
RE C 157250	20.1	141.7	44.0	112	.5	1.8	12.3	782	1.99	1032.0	10.2	49.8	20.6	222	.7	1.8	2.1	22	1.52	.058	27	7.5	.30	135	.020	3	1.40	.022	.22	.8	.01	2.1	.3	.92	4	.6	-
RRE C 157250	16.4	137.8	48.8	139	.6	1.9	13.4	845	2.14	1253.5	11.8	64.8	23.7	232	.9	2.2	1.9	24	1.67	.062	29	6.5	.32	140	.023	1	1.45	.024	.23	.6	.01	2.3	.3	1.03	4	.6	-
C 157251	56.5	92.6	9.5	63	.1	2.3	6.4	628	1.71	10.5	12.5	.7	20.9	171	.2	.6	1.4	18	1.23	.060	35	6.4	.28	108	.017	1	1.36	.026	.21	1.1	<.01	2.1	.2	.53	4	<.5	1700
C 157252	7.0	81.5	10.6	231	.1	2.3	5.3	548	1.74	12.1	8.8	<.5	18.5	208	1.3	.7	1.5	26	.98	.067	44	6.0	.37	135	.020	1	1.45	.035	.17	.3	.01	2.3	.2	.14	5	<.5	2000
C 157253	27.8	16.1	6.5	51	<.1	1.6	4.3	459	1.58	4.9	14.2	2.0	18.7	544	.1	.3	.3	27	.88	.057	34	6.8	.33	267	.032	1	1.17	.036	.19	.6	.01	2.1	.2	.15	4	<.5	2100
C 157254	10.4	53.6	7.8	36	.1	2.3	6.1	570	1.71	9.7	8.2	<.5	28.0	956	.1	.6	2.3	27	1.56	.053	28	6.4	.46	360	.016	<.1	1.67	.022	.20	.8	<.01	2.3	.3	.39	6	<.5	1900
C 157255	216.4	84.2	7.6	79	.1	3.2	7.2	585	1.26	5.7	18.1	.8	20.1	96	.2	.4	1.1	13	1.89	.059	51	7.3	.18	40	.010	2	.96	.016	.14	1.1	<.01	1.4	.2	.67	3	.5	2000
C 157256	773.7	10.7	34.9	11	.1	.3	3.6	842	2.17	7.0	27.1	3.2	14.6	50	<.1	.2	.4	4	1.90	.046	23	2.8	.11	45	<.001	3	.40	.015	.16	.8	<.01	.9	.2	1.83	2	.8	1500
C 157257	428.3	169.1	8.2	29	.1	14.2	9.5	670	2.21	14.3	13.2	1.7	17.4	125	<.1	.3	.5	43	1.18	.067	83	21.4	.78	80	.038	<.1	1.60	.020	.36	.9	.02	4.4	.4	.74	7	.8	1600
C 157258	375.8	9.9	19.3	16	.1	.7	2.1	524	2.18	7.3	17.4	2.0	17.2	68	<.1	.2	.4	13	1.12	.049	29	4.5	.21	73	.010	1	.55	.024	.16	.6	<.01	1.3	.1	1.46	2	<.5	1800
C 157259	35.2	31.6	9.0	23	.1	1.8	2.7	946	1.22	6.7	8.2	<.5	16.9	78	.1	.4	1.1	13	1.62	.053	25	6.2	.24	58	.002	4	.64	.023	.14	11.3	.01	1.5	.2	.18	3	<.5	1200
C 157260	6.7	148.9	1612.6	445	2.7	.9	2.7	377	1.91	1684.1	6.8	35.9	19.7	338	4.1	1.8	1.0	15	.85	.051	17	5.5	.26	139	.010	<.1	.64	.031	.16	.7	.01	1.3	.2	1.02	3	<.5	2300
C 157261	2.0	153.6	864.3	23	2.7	2.1	5.0	505	1.70	38.3	7.8	5.7	17.6	66	.2	.8	9.5	5	1.06	.049	23	5.3	.18	55	.004	2	.66	.018	.16	2.9	<.01	1.1	.2	1.21	2	<.5	1400
C 157262	1.7	24.1	56.4	38	.3	1.2	1.6	850	1.46	21.2	6.9	3.4	17.4	96	.2	.4	.7	17	1.30	.059	21	5.3	.22	186	.016	<.1	.65	.032	.17	.8	.01	1.7	.2	.13	3	<.5	1200
C 157263	4.8	229.6	632.0	76	12.9	2.2	12.9	1016	2.76	1768.7	4.3	59.8	17.2	74	.8	4.4	43.5	6	1.60	.054	23	5.3	.17	56	.010	3	.69	.013	.21	1.1	.02	1.2	.3	2.09	2	.7	1400
C 157264	7.0	76.0	1119.6	301	7.6	.7	4.5	2423	2.28	1159.7	6.8	20.9	16.8	88	3.1	9.6	15.8	5	2.58	.059	22	3.2	.13	107	.004	5	.66	.012	.17	.7	.02	1.4	.2	.89	2	<.5	2300
C 157265	3.0	102.9	1266.7	431	11.7	1.1	13.5	1085	2.01	234.4	5.2	10.6	18.2	150	3.8	.9	71.7	6	1.20	.052	25	4.7	.22	124	.002	2	.79	.014	.18	.6	.01	1.1	.2	1.04	3	<.5	2100
STANDARD DS5	12.5	138.4	23.8	131	.3	24.3	11.8	743	2.87	18.0	5.8	41.7	2.6	46	5.6	3.8	6.0	58	.73	.089	11	178.1	.65	138	.092	17	2.01	.031	.13	5.1	.18	3.3	1.1	<.05	6	5.2	-

Sample type: CORE R150 60C. Samples beginning 'RE' are Reruns and 'RRE' are Reject Reruns.



SAMPLE#	Mo ppm	Cu ppm	Pb ppm	Zn ppm	Ag ppm	Ni ppm	Co ppm	Mn ppm	Fe %	As ppm	U ppm	Au ppb	Th ppm	Sr ppm	Cd ppm	Sb ppm	Bi ppm	V ppm	Ca %	P %	La ppm	Cr ppm	Mg %	Ba ppm	Ti %	B ppm	Al %	Na %	K %	W ppm	Hg ppm	Sc ppm	Tl ppm	S %	Ga ppm	Se ppm	Sample gm
C 157266	.9	11.3	17.2	30	.1	2.4	3.7	1098	1.76	15.8	7.1	5.7	19.0	119	.1	.2	.5	13	1.29	.057	32	4.7	.30	59	.013	1	1.23	.012	.19	.6	<.01	1.3	.2	.32	3	<.5	1200
C 157267	117.2	48.4	139.9	41	3.2	1.5	7.0	831	2.25	62.0	14.7	21.1	20.6	111	.4	.6	14.4	16	1.09	.066	27	3.7	.23	63	.007	<1	1.13	.013	.21	.5	.01	1.4	.2	1.28	3	.5	1300
C 157268	136.8	2353.2	102.5	46	5.9	1.1	4.2	1977	2.41	10.2	5.8	8.6	19.7	97	1.1	3.1	88.8	8	2.60	.057	34	4.4	.18	42	.002	8	.91	.004	.15	.9	<.01	1.8	.2	.68	4	.9	1700
C 157269	12.3	125.8	191.2	122	1.9	1.2	3.4	825	1.85	36.7	6.7	1.1	17.6	100	1.5	2.4	7.1	18	1.86	.069	39	4.5	.19	59	.004	<1	.75	.018	.12	12.8	<.01	2.0	.1	.41	3	<.5	2300
C 157270	2.6	106.7	1334.5	825	2.3	2.7	4.7	781	2.28	659.1	7.0	75.9	19.0	67	11.4	5.0	2.6	27	1.37	.075	32	8.0	.27	79	.027	3	.78	.032	.20	3.9	.02	2.2	.2	.69	4	<.5	2500
C 157271	1.5	61.1	1419.4	236	2.2	1.5	3.6	581	1.93	137.1	8.5	13.3	19.4	55	2.2	3.0	2.4	29	.95	.073	23	6.2	.33	66	.050	4	.61	.028	.16	1.1	<.01	2.0	.1	.31	4	<.5	2100
C 157272	5.0	48.5	393.0	192	.7	3.4	58.8	449	3.18	1692.5	6.6	29.1	18.4	50	1.4	2.5	2.5	27	.87	.071	22	9.1	.34	65	.046	2	.59	.035	.15	3.4	.01	1.6	.1	1.96	3	2.0	2600
C 157273	2.8	50.1	865.3	132	1.1	1.4	3.9	685	1.60	255.6	7.0	5.8	19.9	91	1.3	3.3	2.5	25	1.20	.072	26	6.6	.34	77	.049	4	.71	.027	.17	1.4	.01	1.9	.1	.32	3	<.5	1500
C 157274	38.2	102.2	714.1	821	.9	4.3	5.3	708	2.30	201.6	6.1	21.0	18.8	83	7.7	1.4	.7	27	1.15	.078	26	8.0	.38	83	.047	1	.80	.035	.20	>200	.12	2.2	.2	.62	4	.5	2100
C 157275	3.5	86.8	1027.5	316	1.3	1.7	7.0	498	2.53	30.7	5.8	4.1	19.2	83	3.1	1.1	.8	28	.91	.075	25	6.8	.34	98	.040	3	.68	.032	.19	1.8	.01	2.1	.2	.98	4	<.5	1600
C 157318	26.2	57.6	52.6	1839	.2	3.0	19.0	2576	1.78	13.1	3.3	<.5	18.4	36	21.2	4.6	.3	19	.68	.052	38	6.4	.25	134	.012	<1	1.12	.022	.15	1.5	<.01	1.5	.2	.21	4	.7	1800
RE C 157318	25.5	59.3	51.6	1872	.1	2.9	19.6	2617	1.81	13.5	3.2	<.5	19.0	37	21.6	4.9	.2	18	.68	.054	38	6.8	.25	140	.010	<1	1.09	.022	.15	1.5	<.01	1.5	.2	.21	4	1.2	-
RRE C 157318	30.3	61.1	64.1	2029	.1	2.7	19.3	2641	1.92	14.7	3.1	<.5	19.3	38	22.6	4.9	.3	20	.74	.053	37	4.9	.27	130	.013	1	1.16	.018	.14	.7	.01	1.6	.2	.23	4	.9	-
C 157319	137.9	618.1	779.0	2793	.8	2.5	9.3	3893	2.30	275.7	7.9	1.3	17.5	15	64.0	16.7	.5	9	.24	.056	35	5.0	.11	63	.001	4	.65	.007	.22	1.4	.02	.9	.3	.44	2	.7	2100
C 157323	31.1	1124.5	3020.5	1152	7.2	1.6	4.2	701	3.27	1400.0	14.3	2.3	19.0	109	30.7	62.1	.5	15	.20	.060	31	4.3	.13	214	.011	2	.89	.012	.22	.7	.03	1.7	.2	.06	3	.6	1700
STANDARD DS5	12.2	136.9	23.0	131	.3	23.1	11.8	758	2.97	17.8	5.7	41.1	2.5	45	5.7	3.5	5.9	58	.73	.088	11	178.3	.65	135	.098	17	2.05	.032	.13	4.9	.20	3.4	1.0	<.05	6	4.5	-

Sample type: CORE R150 60C. Samples beginning 'RE' are Reruns and 'RRE' are Reject Reruns.

AA
LL

GEOCHEM PRECIOUS METALS ANALYSIS

Grid Capital Corporation PROJECT AM1 File # A304858 Page 1
1075 Duchess Ave, West Vancouver BC V7T 1G8 Submitted by: Leo KingAA
LL

SAMPLE#	Au** ppb	Sample gm
SI	<2	-
C 157276	5	1700
C 157277	4	1700
C 157278	5	1500
C 157279	5	2100
C 157280	7	1900
C 157281	<2	2500
C 157282	4	2400
C 157283	3	2500
C 157284	2	2500
C 157285	2	2300
C 157286	3	3500
C 157287	<2	3600
C 157288	6	2200
C 157289	3	2900
C 157290	6	3100
RE C 157290	8	-
RRE C 157290	4	-
C 157291	5	3400
C 157292	4	3500
C 157293	3	3700
C 157294	5	3300
C 157295	2	4000
C 157296	3	3900
C 157297	12	3800
C 157298	7	3500
C 157299	4	3700
C 157300	4	3300
C 157301	6	3800
C 157302	3	4200
C 157303	3	3600
C 157304	6	3800
C 157305	3	4000
C 157306	7	3500
C 157307	5	3000
C 157308	6	3700
STANDARD AU-R	492	-

GROUP 3B - FIRE GEOCHEM AU - 30 GM SAMPLE FUSION, DORE DISSOLVED IN AQUA - REGIA, ICP ANALYSIS. UPPER LIMITS = 10 PPM.
- SAMPLE TYPE: CORE R150 60C Samples beginning 'RE' are Reruns and 'RRE' are Reject Reruns.

DATE RECEIVED: OCT 7 2003 DATE REPORT MAILED: Oct 23/2003 SIGNED BY: [Signature] D. TOYE, C. LEONG, J. WANG; CERTIFIED B.C. ASSAYERS

All results are considered the confidential property of the client. Acme assumes the liabilities for actual cost of the analysis only.

Data LFA 11/11



SAMPLE#	Au** ppb	Sample gm
C 157309	9	3500
C 157310	4	1700
C 157311	8	2800
C 157312	2	3300
C 157313	2	3900
C 157314	7	3800
C 157315	2	3600
C 157316	5	1000
C 157317	3	1200
STANDARD AU-R	495	-

Sample type: CORE R150 60C.

ASSAY CERTIFICATE

AA
11

AA
11

Grid Capital Corporation PROJECT AM1 File # A304859
1075 Duchess Ave, West Vancouver BC V7T 1G8 Submitted by: Leo King

SAMPLE#	Pb %	Ag** gm/mt	Au** gm/mt	Sample gm
SI	<.01	<.3	<.01	-
C 157320	1.94	64.5	.23	1000
C 157321	62.34	3099.4	1.38	1200
C 157322	9.50	1770.0	1.05	1000
STANDARD R-2/AU-1	1.48	152.5	3.30	-

GROUP 7AR - 1.000 GM SAMPLE, AQUA - REGIA (HCL-HNO3-H2O) DIGESTION TO 100 ML, ANALYSED BY ICP-ES.
AG** & AU** BY FIRE ASSAY FROM 1 A.T. SAMPLE.
- SAMPLE TYPE: CORE R150 60C

DATE RECEIVED: OCT 7 2003 DATE REPORT MAILED: *Oct 23 / 2003* SIGNED BY: *[Signature]* D. TOYE, C. LEONG, J. WANG; CERTIFIED B.C. ASSAYERS

