ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016 - 510 West Hastings Street
Vancouver, B.C. V6B 1L8
Telephone: 604-688-2568 Fax: 604-688-2578

ASSESSMENT REPORT

describing

PROSPECTING, MAPPING, GEOCHEMICAL SAMPLING, GEOPHYSICAL SURVEYS AND DIAMOND DRILLING

at the

RICH PROPERTY

Rich 1-46 YC45138-YC45185
49-186 YC45388-YC45525

NTS 116I/08
Latitude 66º19'N; Longitude 136º14'W

in the

Dawson Mining District
Yukon Territory

prepared by

Archer, Cathro & Associates (1981) Limited

for

SOUTHAMPTON VENTURES INC.
and
STRATEGIC METALS LTD.

by

Matthew R. Dumala, B.A.Sc., EIT
December 2007

TABLE OF CONTENTS

INTRODUCTION	1
PROPERTY LOCATION, CLAIM DATA AND ACCESS	1
HISTORY	1
GEOMORPHOLOGY	2
REGIONAL GEOLOGY	2
PROPERTY GEOLOGY	3
MINERALIZATION AND GEOCHEMISTRY	4
AIRBORNE GEOPHYSICS	5
DIAMOND DRILLING	5
DISCUSSION AND CONCLUSIONS	9
REFERENCES	11

APPENDICES

I STATEMENT OF QUALIFICATIONS

II CERTIFICATES OF ANALYSIS

III ROCK SAMPLE DESCRIPTIONS

IV GEOPHYSICAL REPORT

V GEOLOGICAL AND GEOTECHNICAL LOGS

FIGURES

No.	Description	Follows Page
1	Property Location	1
2	Claim Location	1
3	Tectonic Setting	2
4	Property Geology	3
5	Stratigraphic Section	3
6	Sample Location	in pocket
7	Nickel/Zinc Geochemistry	in pocket
8	Molybdenum/Copper Geochemistry	in pocket
9	Drill Plan	5

TABLES

No.	Description	Page
I	Regional Lithological Descriptions	2
II	Chip Sample Assay Data	5
III	Drill Hole Data	6
IV	Significant Diamond Drill Hole Intervals	8
V	RI07-08 NiMo Samples	8

INTRODUCTION

The Rich property hosts a thin, sheet-like massive sulphide layer enriched with nickel, molybdenum and zinc. It is located in north-central Yukon and is owned 100% by Strategic Metals Ltd. The property and seven others are under option to Southampton Ventures Inc. as part of the NiMo Project.

This report describes exploration work that was conducted between June 5 and August 24, 2007 by Archer, Cathro & Associates (1981) Limited on behalf of Southampton Ventures. The work was supervised by the author and consisted of prospecting, mapping, geochemical sampling, geophysical surveys and diamond drilling. The author's statement of qualifications appears in Appendix I.

PROPERTY LOCATION, CLAIM DATA AND ACCESS

The Rich property consists of 186 contiguous mineral claims located in north-central Yukon Territory on NTS map sheet 116I/08 at latitude 66˚19'N and longitude 136˚14'W (Figure 1). The claims are registered with the Dawson Mining Recorder in the name of Archer Cathro, which holds them in trust for Strategic Metals. Claim data are listed below while the locations of individual claims are shown on Figure 2.

Claim Number	Grant Number	Expiry Date*
Rich 1-48	YC45138-YC45185	February 22, 2012
49-161	YC45388-YC45500	February 22, 2012
162-186	YC52501-YC52525	February 22, 2012

* Expiry dates include 2007 work which has been filed for assessment credit but not yet accepted.

The Rich property is located 23 km east of Eagle Plains Lodge, which is accessible via the Yukon highway system using the Klondike Highway and Dempster Highway. Eagle Plains is situated 866 km by road north of Whitehorse.

In 2007, daily access to the property was provided by Bell 206B, Bell 206L and Hughes 500D helicopters operated by Fireweed Helicopters Ltd. from Eagle Plains Lodge.

HISTORY

The potential for nickel-molybdenum-zinc rich mineralization along the contact between the Earn and Road River Groups within the Eagle Plain Basin was first recognized during a mineral potential assessment conducted by the Yukon Geological Survey in 1997 (Héon, 2006). This assessment identified a number of stream sediment anomalies over which Strategic staked the Rich property in 2006.

Little mineral exploration has been conducted in the immediate vicinity of the Rich property. The closest significant work programs in 2007 were at the Nor property, 40 km to the southeast

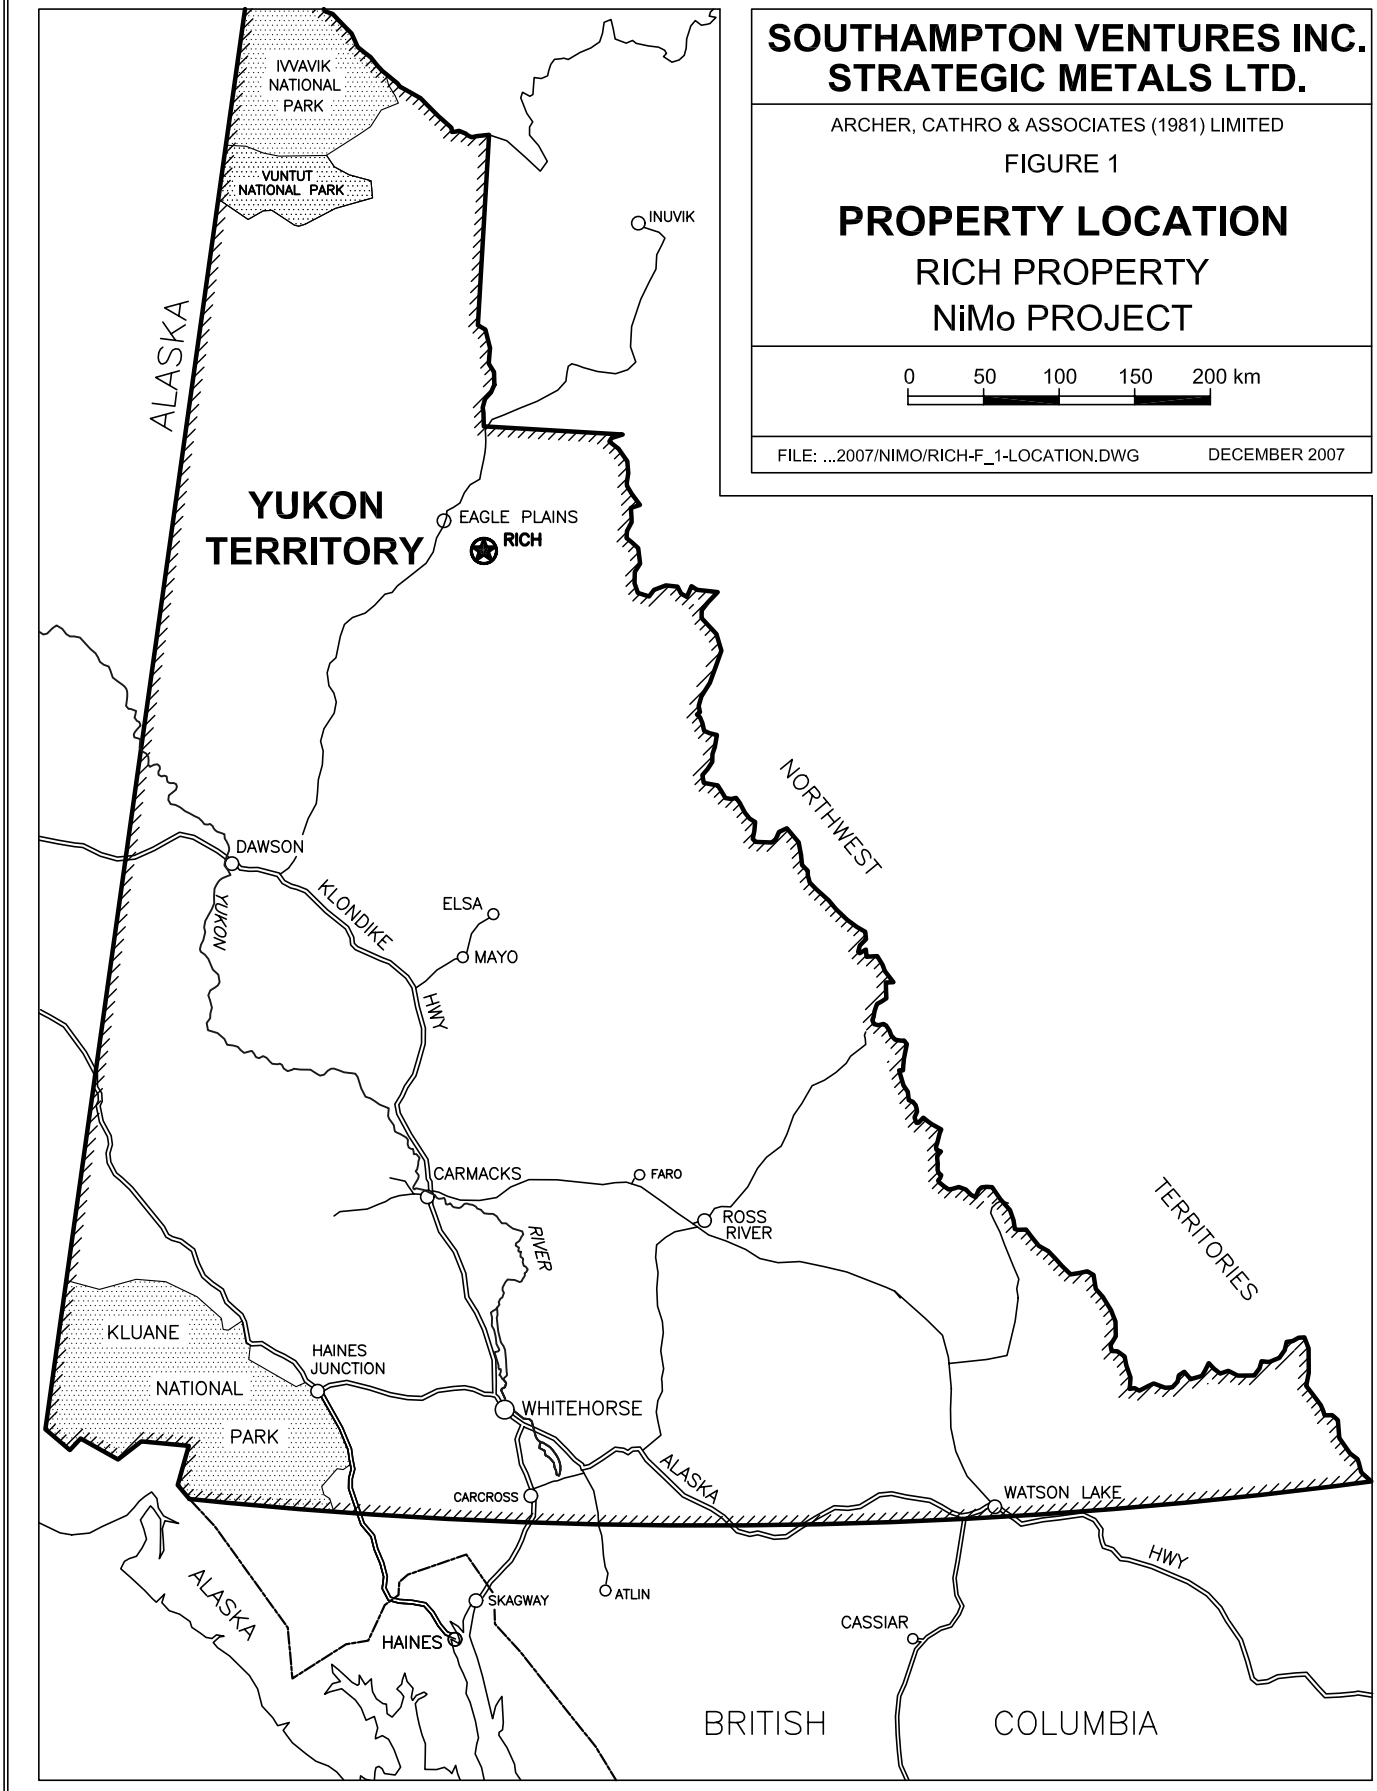
SOUTHAMPTON VENTURES INC.
STRATEGIC METALS LTD.
ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
FIGURE 1
PROPERTY LOCATION
RICH PROPERTY
NiMo PROJECT
0 50 100 150 200 km
FILE: ...2007/NIMO/RICH-F_1-LOCATION.DWG
DECEMBER 2007
IVVAVIK NATIONAL PARK
VUNTUT NATIONAL PARK
INUVIK
ALASKA
YUKON TERRITORY
EAGLE PLAINS
RICH
NORTHWEST
TERRITORIES
DAWSON
YUKON
KLONDIKE
HWY
ELSA
MAYO
CARMACKS
FARO
ROSS RIVER
RIVER
KLUANE
NATIONAL
PARK
HAINES JUNCTION
WHITEHORSE
CARCROSS
ALASKA
WATSON LAKE
HWY
ATLIN
SKAGWAY
HAINES
ALASKA
CASSIAR
BRITISH
COLUMBIA

442 000 mE
444 000 mE
446 000 mE
448 000 mE
7 360 000 mN
7 358 000 mN
7 356 000 mN
7 354 000 mN
7 352 000 mN
7 350 000 mN

T.N.
1°09'
26°20'
Grid north
Magnetic north
Annual change decreasing 30'

RICH 149 YC45488	RICH 150 YC45489	RICH 185 YC52524	RICH 186 YC52525				
RICH 147 YC45486	RICH 148 YC45487	RICH 183 YC52522	RICH 184 YC52523				
RICH 145 YC45484	RICH 146 YC45485	RICH 47 YC45184	RICH 48 YC45185				
RICH 143 YC45482	RICH 144 YC45483	RICH 45 YC45182	RICH 46 YC45183	RICH 181 YC52520	RICH 182 YC52521		
RICH 141 YC45480	RICH 142 YC45481	RICH 43 YC45180	RICH 44 YC45181	RICH 179 YC52518	RICH 180 YC52519		
RICH 139 YC45478	RICH 140 YC45479	RICH 41 YC45178	RICH 42 YC45179	RICH 177 YC52516	RICH 178 YC52517	RICH 175 YC52514	RICH 176 YC52515
RICH 137 YC45476	RICH 138 YC45477	RICH 39 YC45176	RICH 40 YC45177	RICH 35 YC45172	RICH 36 YC45173	RICH 173 YC52512	RICH 174 YC52513
RICH 135 YC45474	RICH 136 YC45475	RICH 37 YC45174	RICH 38 YC45175	RICH 33 YC45170	RICH 34 YC45171	RICH 171 YC52510	RICH 172 YC52511
		RICH 133 YC45472	RICH 134 YC45473	RICH 31 YC45168	RICH 32 YC45169	RICH 169 YC52508	RICH 170 YC52509
		RICH 131 YC45470	RICH 132 YC45471	RICH 29 YC45166	RICH 30 YC45167	RICH 167 YC52506	RICH 168 YC52507
			RICH 129 YC45468	RICH 130 YC45469	RICH 27 YC45164	RICH 28 YC45165	RICH 165 YC52504	RICH 166 YC52505
			RICH 127 YC45466	RICH 128 YC45467	RICH 25 YC45162	RICH 26 YC45163	RICH 163 YC52502	RICH 164 YC52503
			RICH 125 YC45464	RICH 126 YC45465	RICH 23 YC45160	RICH 24 YC45161	RICH 161 YC45500	RICH 162 YC52501
			RICH 123 YC45462	RICH 124 YC45463	RICH 21 YC45158	RICH 22 YC45159	RICH 159 YC45498	RICH 160 YC45499
				RICH 121 YC45460	RICH 122 YC45461	RICH 19 YC45156	RICH 20 YC45157	RICH 157 YC45496	RICH 158 YC45497
				RICH 119 YC45458	RICH 120 YC45459	RICH 17 YC45154	RICH 18 YC45155	RICH 155 YC45494	RICH 156 YC45495
				RICH 117 YC45456	RICH 118 YC45457	RICH 15 YC45152	RICH 16 YC45153	RICH 153 YC45492	RICH 154 YC45493
				RICH 115 YC45454	RICH 116 YC45455	RICH 13 YC45150	RICH 14 YC45151	RICH 151 YC45490	RICH 152 YC45491
				RICH 113 YC45452	RICH 114 YC45453	RICH 11 YC45148	RICH 12 YC45149	RICH 7 YC45144	RICH 8 YC45145
				RICH 111 YC45450	RICH 112 YC45451	RICH 9 YC45146	RICH 10 YC45147	RICH 5 YC45142	RICH 6 YC45143
				RICH 109 YC45448	RICH 110 YC45449	RICH 87 YC45426	RICH 88 YC45427	RICH 3 YC45140	RICH 4 YC45141
				RICH 107 YC45446	RICH 108 YC45447	RICH 85 YC45424	RICH 86 YC45425	RICH 1 YC45138	RICH 2 YC45139
				RICH 105 YC45444	RICH 106 YC45445	RICH 83 YC45422	RICH 84 YC45423	RICH 65 YC45404	RICH 66 YC45405
				RICH 103 YC45442	RICH 104 YC45443	RICH 81 YC45420	RICH 82 YC45421	RICH 63 YC45402	RICH 64 YC45403
				RICH 101 YC45440	RICH 102 YC45441	RICH 79 YC45418	RICH 80 YC45419	RICH 61 YC45400	RICH 62 YC45401
				RICH 99 YC45438	RICH 100 YC45439	RICH 77 YC45416	RICH 78 YC45417	RICH 59 YC45398	RICH 60 YC45399
				RICH 97 YC45436	RICH 98 YC45437	RICH 75 YC45414	RICH 76 YC45415	RICH 57 YC45396	RICH 58 YC45397
				RICH 95 YC45434	RICH 96 YC45435	RICH 73 YC45412	RICH 74 YC45413	RICH 55 YC45394	RICH 56 YC45395
				RICH 93 YC45432	RICH 94 YC45433	RICH 71 YC45410	RICH 72 YC45411	RICH 53 YC45392	RICH 54 YC45393
				RICH 91 YC45430	RICH 92 YC45431	RICH 69 YC45408	RICH 70 YC45409	RICH 51 YC45390	RICH 52 YC45391
				RICH 89 YC45428	RICH 90 YC45429	RICH 67 YC45406	RICH 68 YC45407	RICH 49 YC45388	RICH 50 YC45389

SOUTHAMPTON VENTURES INC.
STRATEGIC METALS LTD.

ARCHER, CATHRO & ASSOCIATES (1981) LIMITED

FIGURE 2

CLAIM LOCATION

RICH PROPERTY

NiMo PROJECT

0 0.4 0.8 1.6 2.4 km

UTM ZONE 8W, NAD 83, 116I/08

FILE: ...2007/NIMO/RICH-F_2-CLAIMS.WOR

DATE: DECEMBER 2007

and in the Wernecke Mountains, 125 km to the southeast. Both of these programs explored for IOCG type deposits in Proterozoic basement rocks.

The Eagle Plain Basin, located about 20 km west of the property, was the focus of extensive petroleum exploration between the mid 1950s and mid 1980s. This work included drilling of 33 wells and 9952 line-km of reflection seismic surveys. A total of 83.7 Bcf of natural gas and 11.05 MM bbls of crude oil was identified within the basin (Osadetz, 2005).

GEOMORPHOLOGY

The Rich property is located within foothills on the southwestern edge of the Richardson Mountains. The property is drained by the tributaries of Eagle River, which ultimately flows into the Bering Sea via the Porcupine and Yukon Rivers.

Local elevations range from 530 m in the west to 860 m in the east. Outcrop is only found in some deeply incised drainages and on steep hillsides. Vegetation consists of stunted spruce, buckbrush, moss and grass.

REGIONAL GEOLOGY

The Rich property lies along the western margin of the Richardson Fault Array, a cluster of north-trending curvilinear, near vertical faults. Episodic reactivation of the Richardson Fault Array in Early and Middle Paleozoic formed a north- to northwest-trending intracratonic depression known as the Richardson Trough (Figure 3). Deep water shale and argillaceous limestone of the Ordovician to Silurian Road River Group were deposited within the trough atop Cambrian- and Proterozoic-age strata. Younger Paleozoic sediments unconformably cap the Road River Group within the trough and elsewhere in a surrounding broader basin. The entire stratigraphic section is folded by a large-scale anticline that plunges to the north. This anticline is called the Richardson Anticlinorium and its axis approximately coincides with the centre of the trough. To the east, the Richardson Trough is bound by the Trevor Fault and to the west, by the Deception Fault.

The following table summarizes the main lithologies in the Rich area from youngest to oldest.

Table I: Regional Lithological Descriptions (after Norris, 1975)

QUATERNARY
Fluvial silt, sand and gravel.

-UNCONFORMITY-

PERMIAN
Jungle Creek Formation: mudstone, calcareous, cherty; limestone, and silty micrite.

-UNCONFORMITY-

UPPER CARBONIFEROUS
Ettrain Formation: cherty limestone.

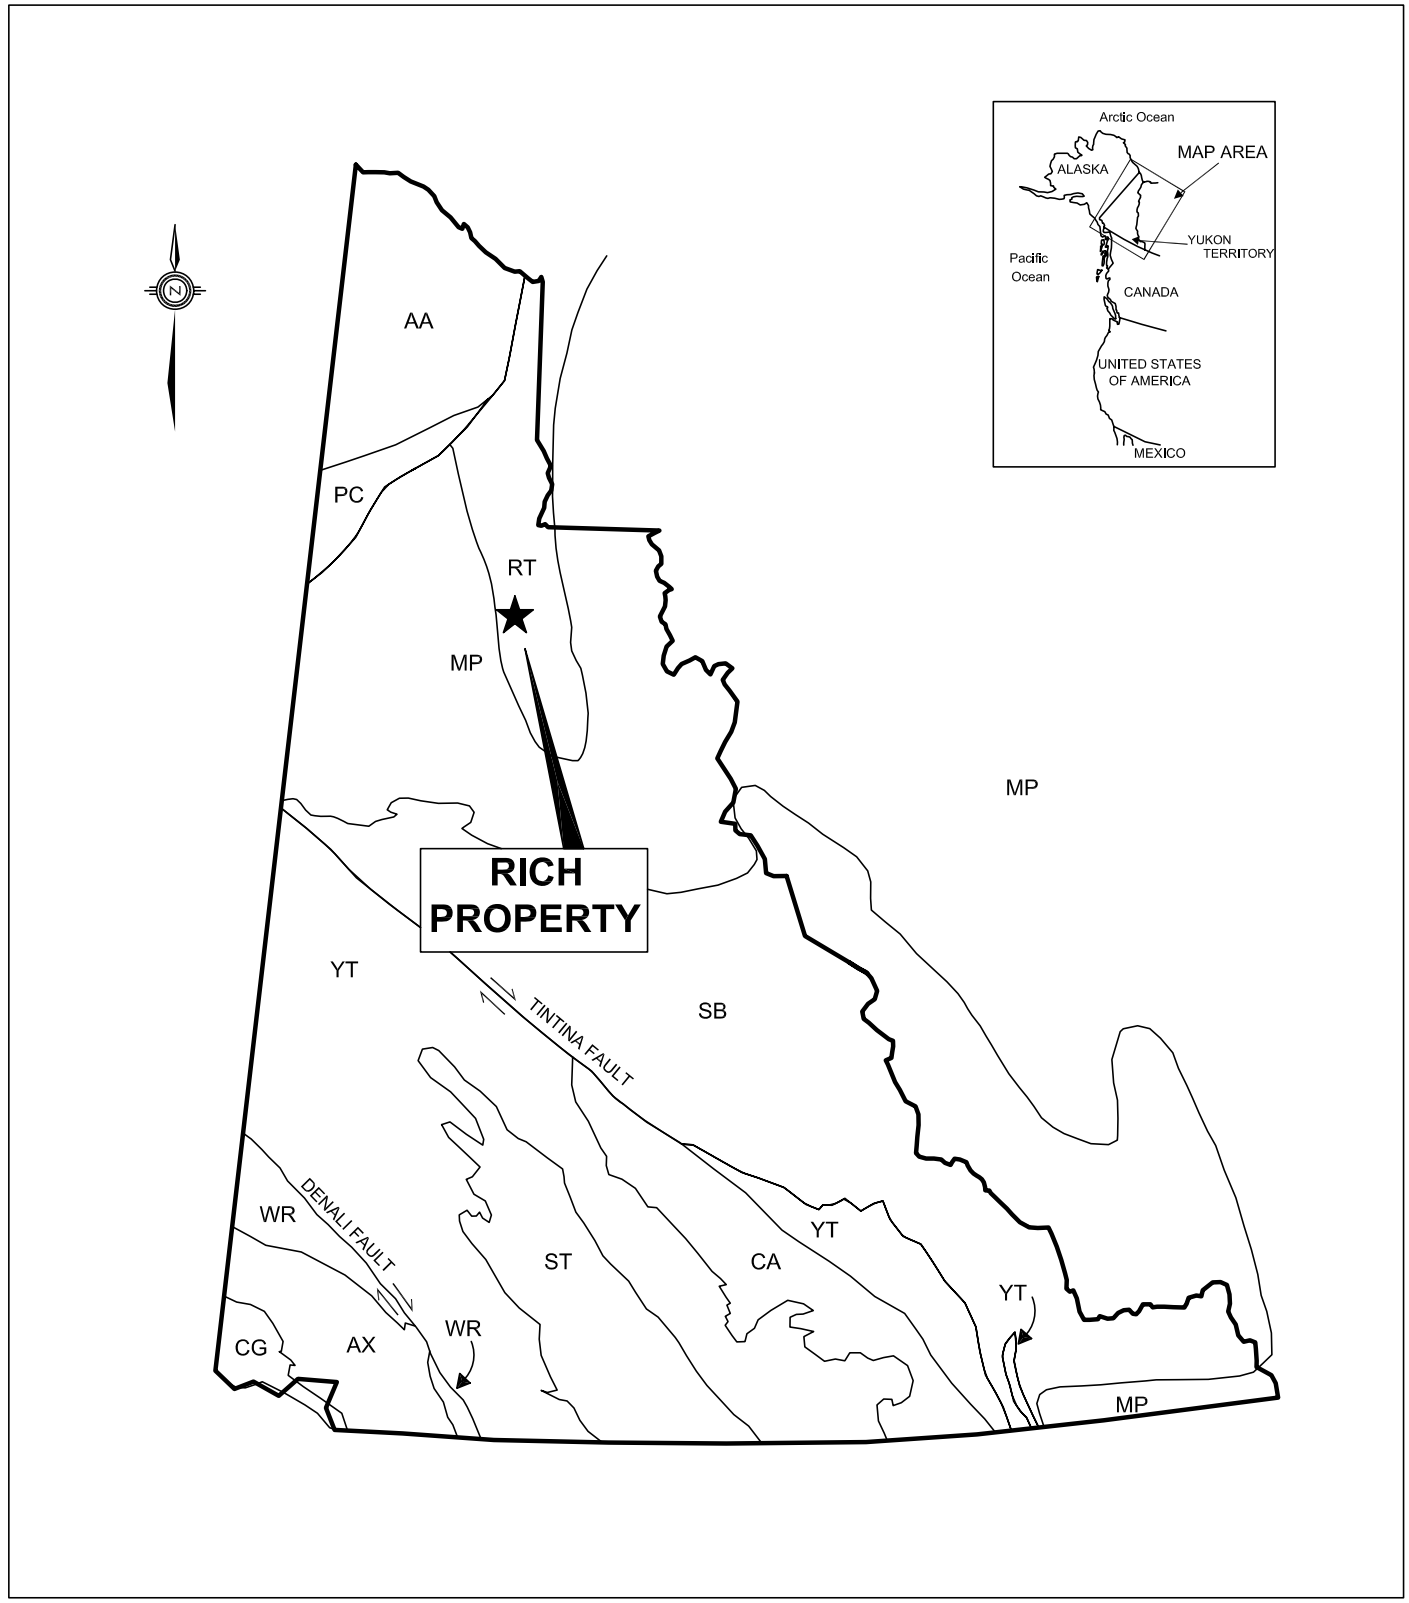

ANCESTRAL NORTH AMERICA

- MP — Mackenzie Platform
- SB — Selwyn Basin
- RT — Richardson Trough

TERRANES
Displaced Continental Margin

- AA — Arctic Alaska
- CA — Cassiar
- PC — Porcupine

Pericratonic Terranes

- YT — Yukon-Tanana / Slide Mountain

ACCRETED TERRANES

- ST — Stikinia / Cache Creek
- AX — Alexander
- WR — Wrangellia
- CG — Chugach

SOUTHAMPTON VENTURES INC.
STRATEGIC METALS LTD.

ARCHER, CATHRO & ASSOCIATES (1981) LIMITED

FIGURE 3

TECTONIC SETTING
RICH PROPERTY
NiMo PROJECT

0 100 200 km

FILE: ...2007\NIMO\RICH\F_3-REGIONAL.DWG

DATE: NOVEMBER 2007

Hart River Formation: limestone, dolomite and chert.

UPPER DEVONIAN TO LOWER CARBONIFEROUS
Ford Lake Shale: siliceous shale, chert and limestone.

MIDDLE TO UPPER DEVONIAN
Earn Group: a conformable marine sequence consisting of upper Imperial Formation and basal Canol Formation. Imperial Formation consists of sandstone, siltstone and shale. The Canol Formation is a sequence of siliceous shale representing a rapid rise of sea level in early Late Devonian.

-UNCONFORMITY-

ORDOVICIAN TO SILURIAN
Road River Group: a 150 to 750 m thick sequence of fossiliferous limestone and calcareous shale.

-UNCONFORMITY-

LOWER AND MIDDLE CAMBRIAN
Slats Creek Formation: siltstone, conglomerate, sandstone and limestone.

PROPERTY GEOLOGY

The Rich property is situated over shallowly (15-25°) west dipping shales (Figure 4), which belong to the Middle to Upper Devonian Earn Group and Ordovician to Silurian Road River Group. The Earn Group includes sandy shale belonging to the Imperial Formation, which is conformably overlain to the east by siliceous shale of the Canol Formation. The Canol Formation forms a narrow north-south band through the centre of the property. The Earn Group sits unconformably above calcareous shale belonging to the Road River Group. Figure 5 shows a generalized stratigraphic section.

The contact between the Earn Group and Road River Group is marked by a distinctive lithological sequence consisting of phosphatic chert member, sulphide horizon, nodular shale and limestone ball member.

The 4 to 8 m thick phosphatic chert member sits at the base of the Canol Formation. It is composed of dark grey weathering, resistant thin to medium bedded cherty shale. Immediately below the phosphatic chert is a massive sulphide horizon that is described in the Mineralization and Geochemistry section in greater detail. Beneath the massive sulphide horizon is a 20 cm to 1.2 m thick nodular shale composed of a black weathering, friable shale containing 5% to 10% barite rich nodules. These nodules range from 1 to 15 cm in diameter.

The underlying limestone ball member is between 1.5 and 10 m thick and consists of black to grey weathering, moderately phosphatic, siliceous shale containing 35% to 40% limestone spheroids. The spheroids consist of laminated micritic limestone ranging from 5 cm to 1.5 m in diameter. Layering within the spheroids is sub-parallel to the adjacent bedding.

SOUTHAMPTON VENTURES INC.
STRATEGIC METALS LTD.

ARCHER, CATHRO & ASSOCIATES (1981) LIMITED

FIGURE 4

PROPERTY GEOLOGY
RICH PROPERTY
NiMo PROJECT

0 2.4 km

UTM ZONE 8W, NAD83
116I08

FILE: ...2007/NIMO/RICH/F_4-GEO.DWG | DATE: DECEMBER 2007

Devonian Imperial Formation

Devonian Canol Formation

Cambrian to Devonian Road River Group

Contact (known, infered)

Normal fault (known, infered)

Thrust fault

True North

1°09'

26°20'

Grid North

Magnetic North

Annual Change Decreasing 30'

7 362 000 mN

7 360 000 mN

7 358 000 mN

7 356 000 mN

7 354 000 mN

7 352 000 mN

7 350 000 mN

Property Boundary

540 000 mE

542 000 mE

544 000 mE

546 000 mE

548 000 mE

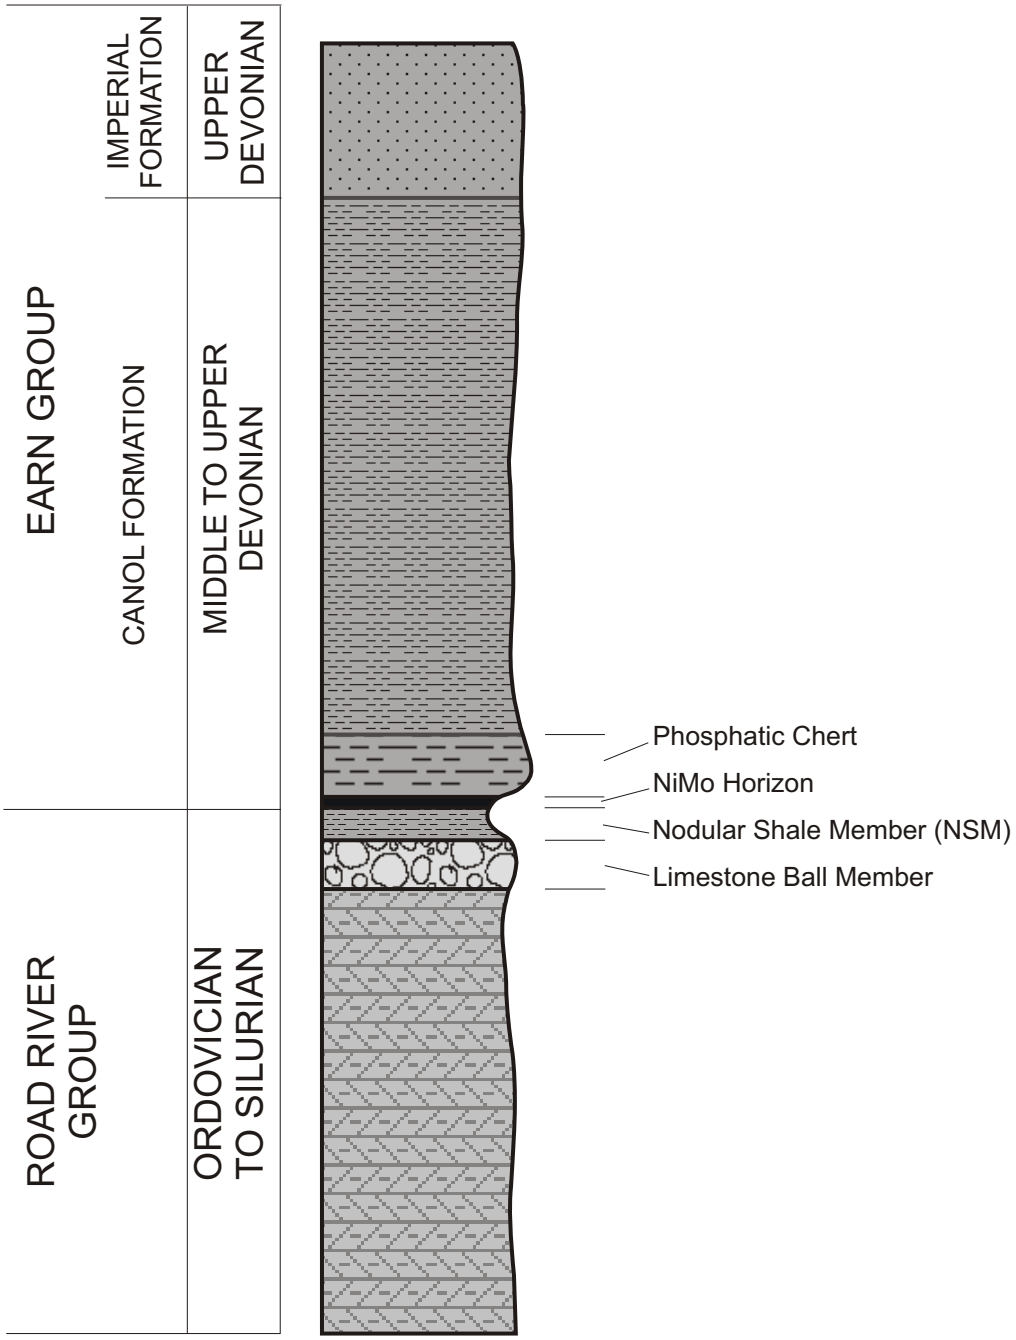

SOUTHAMPTON VENTURES INC.
STRATEGIC METALS LTD.

ARCHER, CATHRO & ASSOCIATES (1981) LIMITED

FIGURE 5

STRATIGRAPHIC SECTION
RICH PROPERTY
NiMo PROJECT

not to scale

...2007/NIMO/RICH/F_5-STRAT.CDR NOVEMBER 2007

MINERALIZATION AND GEOCHEMISTRY

A thin, nickeliferous, massive sulphide layer, known as the NiMo horizon is found along the Canol-Road River contact at the Rich property. This massive sulphide layer is exposed in several deep canyons. The best exposure is in a large canyon on a major drainage, known as Moss Creek, in the centre of the property.

A similar massive sulphide horizon is reported at the same stratigraphic location at the Nick property, 177 km to the southwest. The Nick massive sulphide horizon covers an area greater than 80 km^2 and comprises pyrite, vaesite, melnikovite-type pyrite, sphalerite and wurtzite hosted in a gangue of phosphatic-carbonaceous chert, silica and bitumen (Hulbert et al, 1992). Assays from the Nick horizon average 3.01% nickel, 0.20% molybdenum, 0.82% zinc, 0.82% vanadium, 310 ppb platinum and 150 ppb palladium. Anomalous rhenium (up to 61 ppm), uranium (up to 107.7 ppm), barium (up to 4300 ppm), selenium (up to 2400 ppm) and arsenic (up to 4200 ppm) were also reported. This horizon was the type deposit for exploration at the Rich property.

In 2007, 15 chip, 3 rock specimen, 625 soil and 66 silt samples were collected for the Rich property. All samples were sent to ALS Chemex in North Vancouver. Rock and chip samples were analyzed using the inductively coupled plasma technique for 49 elements (ME-MS61m) plus gold, platinum and palladium (PGM-ICP23). Silt and soil samples were analyzed for 32 elements using the inductively coupled plasma technique (ME-MS41). Samples with selenium exceeding the detection limit were assayed (Se-XRF05). Figure 6 shows the sample locations while geochemical results for nickel/zinc and molybdenum/copper are illustrated on Figures 7 and 8, respectively. Certificates of Analysis appear in Appendix II and Rock Sample Descriptions in Appendix III.

Soil samples were collected at 20 m intervals along lines spaced 200 m apart. These lines were orientated such that they are perpendicular to the Canol-Road River contact. Samples sites are marked with 0.5 m lath and orange flagging. Soil samples yielded average values of 80 ppm nickel, 25 ppm molybdenum and 462 ppm zinc. Samples taken near the surface trace of the NiMo horizon returned anomalous amounts of nickel (up to 1190 ppm), molybdenum (up to 253 ppm), zinc (up to 1.14%), copper (up to 286 ppm) and silver (up to 11.65 ppm). The strongest soil geochemical responses came from the southern half of the property.

Silt samples collected from the various drainages on the property returned average values of 88 ppm nickel, 18 ppm molybdenum, 527 ppm zinc and 0.73 ppm silver with maximums of 287 ppm nickel, 108 ppm molybdenum, 2330 ppm zinc, 504 ppm copper and 2.36 ppm silver. Typically, the strongest responses came from samples collected immediately downstream of the NiMo horizon. However, samples taken from “Moss Creek” returned strongly anomalous values upstream from the exposed NiMo horizon.

Fifteen chip samples were collected from the contact area along four different canyons. Table II summarizes the results of chip samples. Three samples were collected from the NiMo horizon (C38516, C385617 and C385636).

Table II: Chip Sample Assay Data

Sample		Ni	Mo	Zn	Au	Pt	Pd	Re	Ag	As	Se	Tl
	(cm)	(ppm)	(ppm)	(ppm)	(ppb)	(ppb)	(ppb)	(ppm)	(ppm)	(ppm)	(ppm)	(ppm)
C385613	3.5	124.5	168.5	38	165	322	214	31.8	2.27	90.7	162	25.80
C385616	5	4.78%	2380	6170	120	315	196	38.4	2.33	4310	2580	257.00
C385617	1.5	1.29%	2530	189	356	464	296	49.9	4.12	4390	5990	213.00
C385619	1.5	1010	374	2930	27	33	25	3.700	4.79	891	225	14.50
C385620	15	4350	410	5340	18	33	28	4.210	4.47	876	358	20.30
C385621	14	457	28.6	637	3	10	4	0.641	0.29	38	44	2.14
C385622	9	1585	80.6	2130	4	11	4	0.900	0.74	119	70	4.48
C385623	21	7410	783	4500	21	76	37	7.720	4.81	1520	565	36.10
C385624	1.5	198	112	181	256	449	296	48.8	3.6	56	300	14.90
C385625	28	62.1	161.5	27	7	11	3	0.692	0.82	47.8	92	52.60
C385626	0.5	679	349	193	468	638	391	>50	3.96	131	361	62.70
C385634	7	45.3	41.6	87	<1	<5	1	0.049	0.40	31.3	10	4.81
C385635	30	339	22.3	564	<1	<5	2	0.017	0.25	22.9	10	2.62
C385636	8	4.16%	2690	299	241	470	282	>50	3.23	3820	4680	248.00
C385637	28	406	116	23	5	5	6	0.737	0.36	157	131	33.70

AIRBORNE GEOPHYSICS

A helicopter-borne versatile time domain electromagnetic (VTEM) and magnetic survey was conducted over the Rich property in summer 2007 by Geotech Limited of Aurora Ontario, using an AStar B3 helicopter temporarily based at Eagle Plains Lodge. The final report outlining the methods used in this survey and results obtained can be found in Appendix IV.

The electromagnetics show strongest responses in the western part of the property over the Imperial Formation. The NiMo horizon does not appear to be conductive. The magnetic survey shows generally higher susceptibility in the western part of the property but, perhaps most significantly, outlined a weak linear zone of low susceptibility corresponding to the surface trace of the NiMo horizon. Although these surveys appear to have clearly identified the favourable contact, the data are too coarse to pick out subtle variations within the NiMo horizon itself.

DIAMOND DRILLING

General

Drilling was done between July 15 and August 19 and was contracted to North Star Drilling Services Inc. of Delta, BC. The work was completed with two unitized JKS Super-300 diesel powered drills using BTW equipment. A total of 2485.98 m of diamond drilling were completed in 25 holes.

The 2007 holes tested along the Canol-Road River contact over a strike length of 7 km (Figure 9). All drill sites were constructed by hand atop of the natural ground cover, wherever possible, using 6”x 6” timbers. Drill data for the holes is listed in Table II.

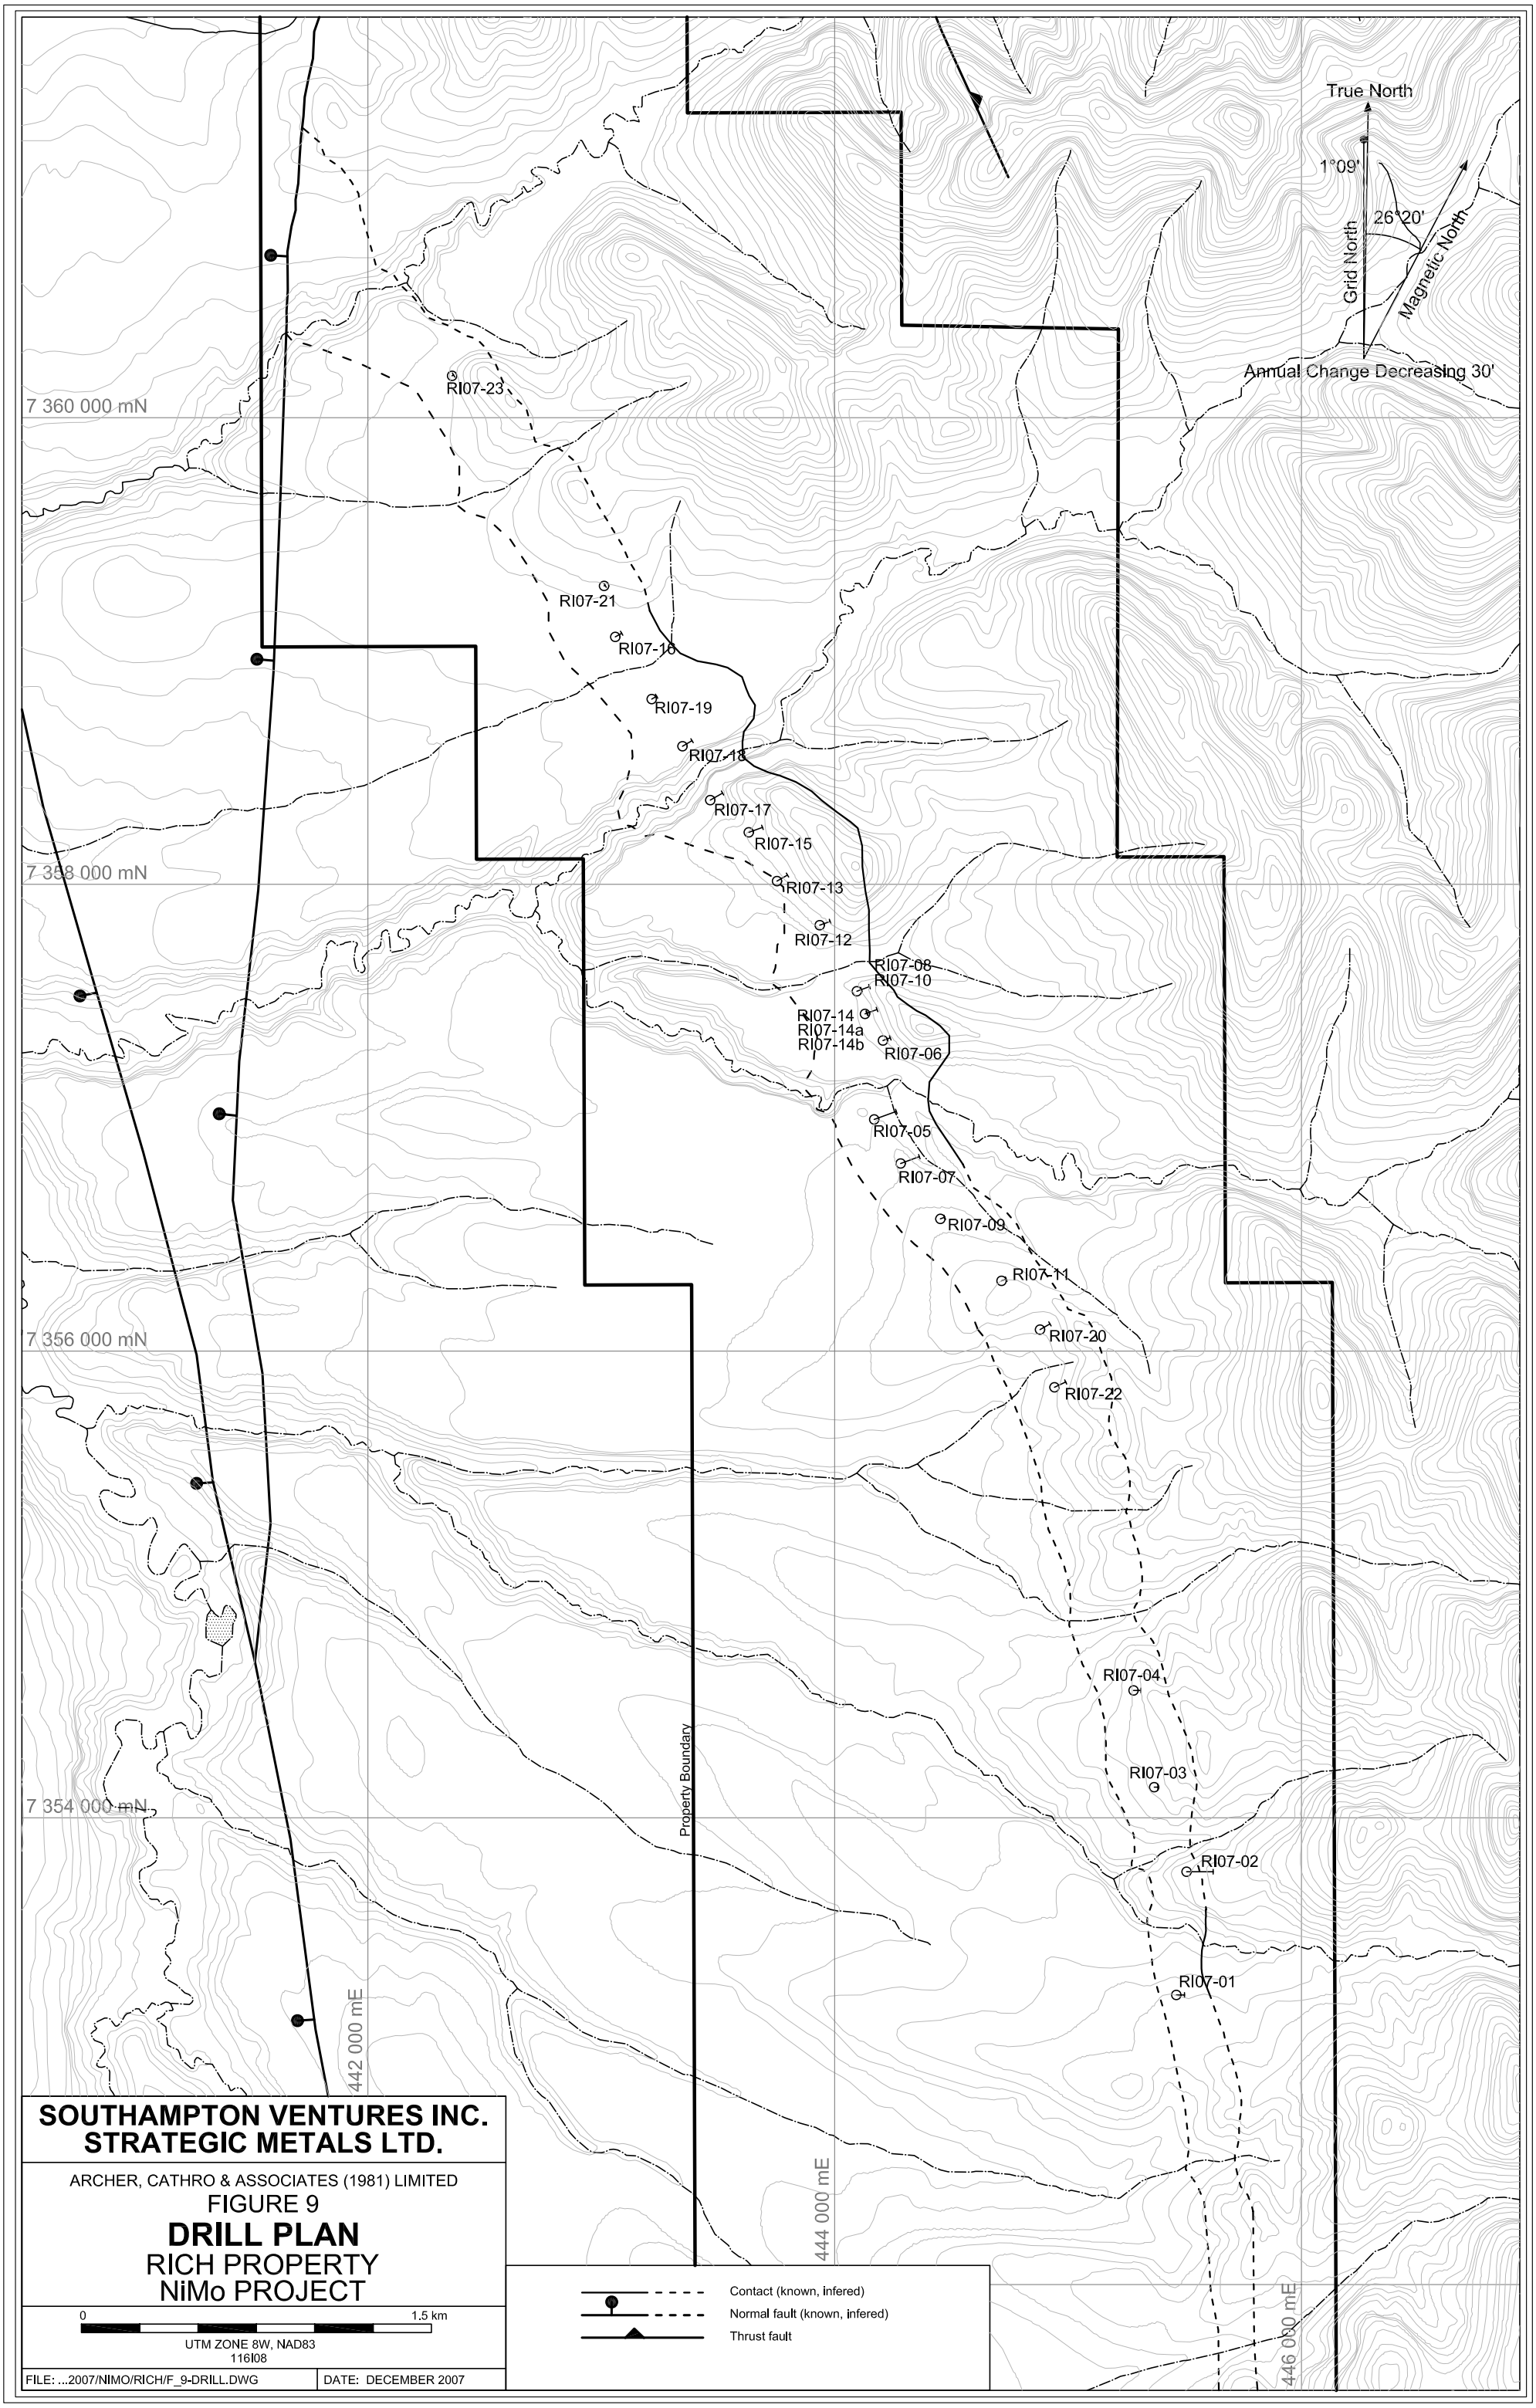
True North
1°09'
26°20'
Grid North
Magnetic North
Annual Change Decreasing 30'
7 360 000 mN
7 358 000 mN
7 356 000 mN
7 354 000 mN
RI07-23
RI07-21
RI07-16
RI07-19
RI07-18
RI07-17
RI07-15
RI07-13
RI07-12
RI07-08
RI07-10
RI07-14
RI07-14a
RI07-14b
RI07-06
RI07-05
RI07-07
RI07-09
RI07-11
RI07-20
RI07-22
RI07-04
RI07-03
RI07-02
RI07-01
Property Boundary
442 000 mE
444 000 mE
446 000 mE
SOUTHAMPTON VENTURES INC.
STRATEGIC METALS LTD.
ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
FIGURE 9
DRILL PLAN
RICH PROPERTY
NiMo PROJECT
0
1.5 km
UTM ZONE 8W, NAD83
116I08
FILE: ...2007/NIMO/RICH/F_9-DRILL.DWG
DATE: DECEMBER 2007
Contact (known, infered)
Normal fault (known, infered)
Thrust fault

Table III: Drill Hole Data

Hole	Easting	Northing	Elevation (m)	Azimuth	Angle	Depth (m)
RI07-01	445464	7353241	679	090°	-55°	60.96
RI07-02	445508	7353769	681	090°	-50°	176.79
RI07-03	445370	7354131	-	090°	-50°	24.38
RI07-04	445280	7354545	-	090°	-50°	48.77
RI07-05	444169	7356993	614	070°	-60°	201.17
RI07-06	444207	7357331	622	070°	-75°	128.02
RI07-07	444283	7356805	621	070°	-60°	170.69
RI07-08	444095	7357542	-	070°	-65°	137.16
RI07-09	444432	7356554	638	070°	-60°	39.62
RI07-10	444095	7357542	-	070°	-75°	82.30
RI07-11	444715	7356301	674	070°	-60°	42.67
RI07-12	443936	7357825	-	070°	-60°	94.49
RI07-13	443753	7358014	-	060°	-60°	103.63
RI07-14	444130	7357445	-	070°	-80°	60.96
RI07-14A	444130	7357445	-	070°	-50°	82.30
RI07-14B	444130	7357445	-	070°	-85°	88.39
RI07-15	443631	7358223	643	060°	-60°	124.97
RI07-16	443096	7359016	606	060°	-75°	121.92
RI07-17	443467	7358361	608	060°	-60°	121.92
RI07-18	443348	7358592	597	060°	-60°	94.49
RI07-19	443218	7358794	594	060°	-75°	94.49
RI07-20	444880	7356092	646	060°	-75°	189.28
RI07-21	443006	7359258	624	060°	-75°	19.81
RI07-22	444942	7355845	-	065°	-70°	155.45
RI07-23	442370	7360184	630	060°	-70°	21.34

Core was transported from the drill sites to a logging area on the property, where recovery was measured and geological and geotechnical logging was performed. Geologically and mineralogically favourable intervals from each hole were transported by helicopter to Eagle Plains where they were sawn with one-half bagged and sent for analysis and the other half returned to the core box. Core boxes containing sawn core were shipped to Whitehorse and placed in storage, all other core is stored on the property. All intersections of NiMo mineralization were removed from the core boxes and placed in airtight bags in order to prevent oxidation. These intersections were shipped to Vancouver for further study and storage. Appendix IV contains the geological and geotechnical logs.

Core samples were transported from Eagle Plains to Whitehorse by truck, escorted by a representative of Archer Cathro. The samples were then shipped to ALS Chemex in North Vancouver. Core samples were dried and crushed to 70% minus 2 mm, before a 1.5 kg split was taken and pulverized to better than 85% minus 75 microns. Splits of the pulverized fraction were routinely dissolved in aqua regia and analyzed for 49 elements using the inductively coupled plasma technique (ME-MS61m). Select samples were also analyzed for gold, platinum and palladium (PGM-ICP23). Due to the small size of the NiMo horizon samples, they were first assayed for nickel (Ni-AA62), molybdenum (Mo-AA62), zinc (Zn-AA62) and rhenium (Re-MS42) before being analyzed for gold, platinum and palladium (PGM-ICP23). Only samples

from RI07-05, -08, -15, -16, -17 and -18 were analyzed for 49 elements (ME-MS61m). Certificates of Analysis are found in Appendix II.

Results

Diamond drilling intersected shales belonging to the Canol Formation and the Road River Group. Deeply and strongly weathered bedrock hampered drilling efforts in the southern half of the property where most of the holes were abandoned before reaching the prospective contact.

In drill core, the Canol Formation shale is black, non-calcareous, and finely laminar. It is slightly to moderately weathered, fissile and somewhat friable. Barite rich nodules, phosphate rich nodules, cherty layers, micrite and carbonate laminae/beds are also present towards the lower contact. The Canol Formation also exhibits rare to common, thinly bedded, sulphide rich laminae and lenses, as well as uncommon to common, finely laminar, non-fossiliferous, grey to black micritic limestone beds up to several centimetres thick.

The Road River Group comprises calcareous, finely laminar, evenly bedded, black shale that is distinguished from shale belong to the Canol Formation by its vigorous reaction with dilute hydrochloric acid. Distinctive brecciated limestone balls commonly occur within one to three metres of the Canol-Road River contact. Lower in the formation, crinoid stem fragments are often found within limestone beds, which exhibit a grainstone texture. The Road River Group also contains finely laminar, fine-grained sulphides (dominantly pyrite) in bands, lenses and beds and in disseminated form.

The NiMo horizon consists of very fine-grained, bronze-to-gold, sulphide-rich laminae. Individual laminae range in thickness from < 1 mm up to about 2 mm. They are wavy and commonly exhibit a pinch-and-swell texture. Mild to moderate bioturbation and physical disruption of individual laminae is characteristic of the horizon. Out of the 14 holes that intersected the Canol-Road River contact, only four did not intersect visible NiMo mineralization. Two of these four holes (RI07-14A and RI07-14B) had poor recovery in the contact zone. The other two holes (RI07-19 and -20) intersected sulphide mineralization near the predicted intersection of the contact; however, samples collected from these intervals returned only weak to moderate values of NiMo indicator elements. The thickness of the NiMo horizon ranges from approximately 1 cm to 196 cm (RI07-08). Excluding the interval in RI07-08 the individual layers of NiMo mineralization averaged 3.5 cm. The NiMo horizon in hole RI07-08 displays signs of soft sediment deformation, while the sediments above and below the horizon appear undeformed.

Except for their varying carbonate content, the Canol Formation and Road River Group are mineralogically similar. Geochemically they are also similar. Barium is often weakly enriched immediately above and/or below the contact, with a slight bias towards the footwall. Strontium also appears to differ between the two units. It typically ranges from 50 to 100 ppm in the Canol compared to 150 to 300 ppm in the Road River.

The NiMo horizon is geochemically and mineralogically distinct from the rocks immediately above and below it. With the exceptions described in the paragraph at the end of this section,

samples collected above and below the favourable contact (up to 14 m above and 20 m below) returned no significant results. Samples collected in the adjacent wallrocks averaged 150 ppm nickel, 40 ppm molybdenum, 400 ppm zinc, 0.05 ppm rhenium, 17 ppm selenium, 8 ppm uranium and 8 ppm cobalt. Zinc showed the most variability, returning up to 2590 ppm. Values for the other elements were confined to a relatively tight range near the average value.

Significant assay results for samples from the NiMo horizon are summarized in Table IV. The NiMo horizon shows an elevated concentrations of nickel, molybdenum, zinc, gold, platinum, palladium, rhenium, arsenic, antimony, cobalt, copper, germanium, indium, phosphorous, selenium, tellurium, thallium and uranium relative to the wallrocks.

Table IV: Significant Diamond Drill Hole Intervals

Hole	From (m)	To (m)	Int. (m)	Ni (%)	Mo (ppm)	Zn (%)	Au (ppb)	Pt (ppb)	Pd (ppb)	Re (ppm)	Se (ppm)	Ag (ppm)
RI07-05	152.56	152.58	0.02	3.90	714	4.25	70	184	156	9.35	1225	1.86
RI07-06	52.37	52.38	0.01	3.30	1000	0.38	234	315	412	10.10	NA	NA
RI07-06	58.62	85.66	0.04	3.91	1250	2.36	96	196	142	13.00	NA	NA
RI07-07	158.64	158.67	0.03	3.60	2500	0.46	97	207	128	29.60	NA	NA
RI07-08*	62.22	64.18	1.96	1.31	1189	0.10	46	92	41	9.68	476	0.46
RI07-10	65.82	65.88	0.06	2.64	1350	0.59	245	148	109	8.80	NA	NA
RI07-12	82.72	82.74	0.02	3.04	1270	0.32	101	186	102	15.95	NA	NA
RI07-12	83.12	83.17	0.05	1.78	930	0.98	71	75	75	12.35	NA	NA
RI07-15	101.50	101.53	0.03	2.66	2820	0.38	100	174	98	17.35	>1000	1.92
RI07-16	91.90	91.91	0.01	4.56	2790	1.05	158	225	152	38.50	>1000	3.85
RI07-17	96.74	96.75	0.01	7.04	2460	1.54	89	254	158	38.60	>1000	2.14
RI07-18	70.68	70.73	0.05	4.30	1720	0.72	79	194	125	29.60	1265	2.06
RI07-19	80.59	80.62	0.03	0.65	237	0.29	17	50	19	3.12	250	0.50
RI07-20	74.42	74.51	0.09	0.080	129.5	0.04	17	5	6	0.47	20	0.34

**weighted average of 20 samples*

Individual samples collected from within the 1.96 m thick NiMo horizon in RI07-08 show a considerable variation of metal values. These variations in metal content suggest that this intersection crosses the horizon, instead of running along it. The samples collected near the top and bottom of the interval are more enriched in most elements, implying a possible second pulse of mineralization. The material between these two enriched layers is more diluted with sediments and shows signs of soft sediment deformation. Individual sample results for the NiMo horizon in RI07-08 are summarized in Table V.

Table V: RI07-08 NiMo Samples

From (m)	To (m)	Int. (cm)	Ni (%)	Mo (ppm)	Zn (%)	Au (ppb)	Pt (ppb)	Pd (ppb)	Re (ppm)	Se (ppm)	Ag (ppm)
62.22	62.22	<1	1.14	766	0.68	331	169	78	1.72	>1000	1.69
62.22	62.29	7	0.47	125.5	0.18	32	58	23	2.11	214	0.32
62.29	62.39	10	1.85	468	0.15	68	129	56	9.20	590	0.74
62.39	62.50	11	2.10	550	0.14	65	152	61	10.15	585	0.76
62.50	62.61	11	1.37	386	0.08	46	113	42	7.81	401	0.42
62.61	62.71	10	1.72	472	0.08	54	122	48	10.50	500	0.52
62.71	62.76	5	1.66	467	0.08	46	114	45	10.25	484	0.51
62.76	62.90	14	0.86	288	0.05	21	45	16	5.76	271	0.29
62.90	63.03	13	0.25	118.5	0.02	14	11	11	2.08	103	0.16

63.03	63.20	17	1.53	398	0.08	37	130	49	10.70	486	0.40
63.20	63.31	11	1.37	434	0.07	70	104	40	11.20	504	0.38
63.31	63.41	10	1.06	511	0.05	75	88	37	9.03	486	0.43
63.41	63.58	17	1.27	377	0.06	61	99	40	11.10	513	0.36
63.58	63.74	16	1.03	324	0.05	50	74	37	9.33	431	0.34
63.74	63.85	11	1.15	270	0.05	33	62	39	12.10	502	0.32
63.85	63.95	10	0.73	187.5	0.04	15	46	25	8.10	328	0.27
63.95	64.00	5	1.89	498	0.13	41	119	72	18.95	899	0.78
64.00	64.08	8	2.85	713	0.25	61	169	105	23.10	>1000	1.14
64.08	64.11	3	1.89	1055	0.99	NA	NA	NA	13.75	960	0.95
64.11	64.18	7	1.12	501	0.25	32	76	37	9.37	539	0.57

Both RI07-06 and RI07-12 contained two distinct NiMo horizons, which were identified visually and geochemically. These holes are located 250 m south and 250 m north of RI07-08, respectively. The two horizons are 6.24 m apart in RI07-06 and 0.38 m apart in RI07-12. Material between the mineralized layers in RI07-06 returned only background values for NiMo indicator elements (151 ppm nickel, 44 ppm molybdenum and 263 ppm zinc), while similar material in RI07-12 yielded moderately anomalous values (3900 ppm nickel, 264 ppm molybdenum and 1030 ppm zinc). Samples collected between the layers also returned low carbonate values and weakly elevated strontium, indicative of Canol Formation.

DISCUSSION AND CONCLUSIONS

The nickel rich, NiMo horizon occurs at a predictable stratigraphic location and has demonstrated considerable lateral continuity. These factors coupled with the horizon's diverse metal suite and consistently high metal values make it an attractive exploration target.

Surface mapping, geochemical sampling and geophysical surveys have traced the NiMo horizon over a 10.5 km strike length on the Rich property. Drilling in 2007 has successfully tested along the NiMo horizon over a strike length of 2.7 km and up to 200 m downdip. The target remains open in three directions (it daylights to the east). Drilling in the southern half of the property near the strongest soil geochemical results was hindered by deeply weathered bedrock and remains untested. Samples of the mineralized layers from the 10 diamond drill holes that intersected the horizon, excluding RI07-08, produced an average of 3.45% nickel, 0.161% molybdenum, 1.10% zinc, 113 ppb gold, 184 ppb platinum, 140 ppb palladium and 18.9 ppm rhenium over 3.5 cm. The NiMo horizon from holes RI07-06, -08 and -12, including the mineralized layers and non- to weakly-mineralized material between them, averaged 0.67% nickel, 0.028% molybdenum, 0.12% zinc, 27 ppb gold, 49 ppb platinum, 22 ppb palladium and 4.7 ppm rhenium over 2.9 m.

Thickening of the NiMo horizon appears to be a result of either local conditions during primary deposition or later soft sediment deformation. The changes in the thickness occur suddenly over short distances and do not appear to be expressed in the hanging wall or footwall stratigraphy.

The uncommonly thick NiMo horizon in RI07-08 includes two especially rich layers surrounding weaker mineralized material. The nearest completed holes (RI07-06 and RI07-12) also cut two metal-rich layers. Holes RI07-10, -14, -14a and -14b were drilled within 100 m of RI07-08; but they did not intersect the NiMo mineralization because of poor core recovery and bad ground conditions near the target depth. It is not clear whether the presence of two metal enriched layers

is due to separate deposition events or structural repeating. Additional drilling near RI07-08 is recommended in order to determine the lateral extent of the thickening, and the continuity and nature of the two mineralized layers.

The subdued topography, deep weathering and thick blanket of glacial and fluvial cover severely limit the effectiveness of surface exploration techniques in tracing and evaluating this mineralization. Drilling has proven to be effective but it must be done before the frost melts and drill pads become unstable. Accordingly, continued widely spaced drilling and detailed drilling are recommended and work should begin in late March.

Respectfully submitted,

ARCHER, CATHRO & ASSOCIATES (1981) LIMITED

Matthew R. Dumala, B.A.Sc. EIT.

REFERENCES

Coveney, R.M., Murowchick, J.B., Grauch, R.I., Nansheng, C. and Glascock, M.D.
1992 Field Relations, Origins, and Resource Implications for Platiniferous Molybdenum-Nickel Ores in Black Shales of South China; Exploration Mining Geology, Vol. 1, No. 1, pp 21-28.

Héon, D
2006 Mineral Assessment of the Eagle Plain Study Area, Yukon; Yukon Geological Survey Open File 2006-3.

Hulbert, L.J., Grégoire, D.C., Paktunc, D. and Carne, R.C.
1992 Sedimentary Nickel, Zinc, and Platinum-group-element Mineralization in Devonian Black Shales at the Nick Property, Yukon, Canada: A New Deposit Type; Exploration Mining Geology, Vol. 1, No. 1, pp 39-62.

Lott, D.A., Coveney, R.M., Murowchick, J.B. and Grauch, R.I.
1999 Sedimentary Exhalative Nickel-Molybdenum Ores in South China; Economic Geology, Vol. 94, pp 1051-1066.

Norris, D.K.
1982 Geology, Hart River (116H), Yukon Territory; Geological Survey of Canada, Map 1527A.

Osadetz, K.G., Chen, Z. and Bird, T.D.
2005 Petroleum Resource Assessment, Eagle Plain Basin and Environs, Yukon Territory, Canada; Yukon Geological Survey Open File 2005-2; Geological Survey of Canada Open File 4922.

APPENDIX I

STATEMENT OF QUALIFICATIONS

STATEMENT OF QUALIFICATIONS

I, Matthew R. Dumala, geological engineer, with business addresses in Vancouver, British Columbia and Whitehorse, Yukon Territory and residential address in Vancouver, British Columbia, do hereby certify that:

1. I graduated from the University of British Columbia in 2002 with a B.A.Sc in Geological Engineering, Option l, mineral and fuel exploration.

2. I am registered as an Engineer in Training in the Province of British Columbia.

3. From 2003 to present, I have been actively engaged in mineral exploration in the Yukon Territory.

4. I have personally participated in the fieldwork reported herein.

Matthew R. Dumala, B.A.Sc., EIT

APPENDIX II

CERTIFICATES OF ANALYSIS

ALS Chemex
EXCELLENCE IN ANALYTICAL CHEMISTRY
ALS Canada Ltd.
212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Finalized Date: 22-NOV-2007
Account: MTT

CERTIFICATE VA07128847

Project: NIMO RICH

P.O. No.:

This report is for 1 Drill Core sample submitted to our lab in Vancouver, BC, Canada on 2-NOV-2007.

The following have access to data associated with this certificate:

JOAN MARIACHER

SAMPLE PREPARATION

ALS CODE	DESCRIPTION
FND-02	Find Sample for Addn Analysis

ANALYTICAL PROCEDURES

ALS CODE	DESCRIPTION	INSTRUMENT
ME-XRF05	Trace Level XRF Analysis	XRF

To: **STRATEGIC METALS LTD.**
ATTN: JOAN MARIACHER
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

This is the Final Report and supersedes any preliminary report with this certificate number. Results apply to samples as submitted. All pages of this report have been checked and approved for release.

Signature:

Lawrence Ng, Laboratory Manager - Vancouver

ALS Chemex
EXCELLENCE IN ANALYTICAL CHEMISTRY
ALS Canada Ltd.
212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO RICH

Finalized Date: 22-NOV-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07128847

Sample Description	Method / Analyte / Units / LOR	ME-XRF05 Se ppm 2
C488230		1310

Comments: Sample #1 is NSS.

ALS Chemex
EXCELLENCE IN ANALYTICAL CHEMISTRY
ALS Canada Ltd.
212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

STRATEGIC METALS LTD.
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Finalized Date: 13-NOV-2007
Account: MTT

CERTIFICATE VA07128846

Project: NIMO RICH

P.O. No.:

This report is for 1 Rock sample submitted to our lab in Vancouver, BC, Canada on 5-NOV-2007.

The following have access to data associated with this certificate:

JOAN MARIACHER

SAMPLE PREPARATION

ALS CODE	DESCRIPTION
FND-02	Find Sample for Addn Analysis

ANALYTICAL PROCEDURES

ALS CODE	DESCRIPTION	INSTRUMENT
ME-XRF05	Trace Level XRF Analysis	XRF

To: **STRATEGIC METALS LTD.**
ATTN: JOAN MARIACHER
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

his is the Final Report and supersedes any preliminary report with this certificate number. Results apply to samples as submitted. All ages of this report have been checked and approved for release.

Signature: Lawrence Ng

Lawrence Ng, Laboratory Manager - Vancouver

ALS Chemex
EXCELLENCE IN ANALYTICAL CHEMISTRY
ALS Canada Ltd.
212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

STRATEGIC METALS LTD.
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO RICH

Finalized Date: 13-NOV-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07128846

Sample Description	Method / Analyte / Units / LOR	ME-XRF05 Se ppm 2
C488304		NSS

Comments: NSS is non-sufficient sample.

ALS Chemex
EXCELLENCE IN ANALYTICAL CHEMISTRY
ALS Canada Ltd.
212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

STRATEGIC METALS LTD.
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Finalized Date: 9-NOV-2007
Account: MTT

CERTIFICATE VA07128844

Project: NIMO RICH

P.O. No.:

This report is for 1 Drill Core sample submitted to our lab in Vancouver, BC, Canada on 5-NOV-2007.

The following have access to data associated with this certificate:

AL ARCHER VANCOUVER OFFICE	DOUG EATON BILL WENGZYNOWSKI	JOAN MARIACHER

SAMPLE PREPARATION

ALS CODE	DESCRIPTION
FND-02	Find Sample for Addn Analysis

ANALYTICAL PROCEDURES

ALS CODE	DESCRIPTION	INSTRUMENT
ME-XRF05	Trace Level XRF Analysis	XRF

To: STRATEGIC METALS LTD.
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

s is the Final Report and supersedes any preliminary report with this certificate number. Results apply to samples as submitted. All es of this report have been checked and approved for release.

Signature:

Lawrence Ng, Laboratory Manager - Vancouver

ALS Chemex
EXCELLENCE IN ANALYTICAL CHEMISTRY
ALS Canada Ltd.
212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

STRATEGIC METALS LTD.
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO RICH

Finalized Date: 9-NOV-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07128844

Sample Description	Method / Analyte / Units / LOR	ME-XRF05 Se ppm 2
C385574		1225

ALS Chemex
EXCELLENCE IN ANALYTICAL CHEMISTRY
ALS Canada Ltd.
212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

T TRATEGIC METALS LTD.
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Finalized Date: 15-NOV-2007
Account: MTT

CERTIFICATE VA07128842

Project: NIMO - RICH

P.O. No.:

This report is for 1 Rock sample submitted to our lab in Vancouver, BC, Canada on 5-NOV-2007.

The following have access to data associated with this certificate:

AL ARCHER VANCOUVER OFFICE	DOUG EATON BILL WENGZYNOWSKI	JOAN MARIACHER

SAMPLE PREPARATION

ALS CODE	DESCRIPTION
FND-02	Find Sample for Addn Analysis

ANALYTICAL PROCEDURES

ALS CODE	DESCRIPTION	INSTRUMENT
ME-XRF05	Trace Level XRF Analysis	XRF

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

This is the Final Report and supersedes any preliminary report with this certificate number. Results apply to samples as submitted. All pages of this report have been checked and approved for release.

Signature: Lawrence Ng

Lawrence Ng, Laboratory Manager - Vancouver

ALS Chemex
EXCELLENCE IN ANALYTICAL CHEMISTRY
ALS Canada Ltd.
212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

T TRATEGIC METALS LTD.
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO - RICH

Finalized Date: 15-NOV-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07128842

Sample Description	Method / Analyte / Units / LOR	ME-XRF05 Se ppm 2
C488360		1265

ALS Chemex
EXCELLENCE IN ANALYTICAL CHEMISTRY
ALS Canada Ltd.
212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

STRATEGIC METALS LTD.
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Finalized Date: 13-NOV-2007
Account: MTT

CERTIFICATE VA07128841

Project: NIMO - RICH

P.O. No.:

This report is for 1 Rock sample submitted to our lab in Vancouver, BC, Canada on 5-NOV-2007.

The following have access to data associated with this certificate:

AL ARCHER VANCOUVER OFFICE	DOUG EATON BILL WENGZYNOWSKI	JOAN MARIACHER

SAMPLE PREPARATION

ALS CODE	DESCRIPTION
FND-02	Find Sample for Addn Analysis

ANALYTICAL PROCEDURES

ALS CODE	DESCRIPTION	INSTRUMENT
ME-XRF05	Trace Level XRF Analysis	XRF

To: STRATEGIC METALS LTD.
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

his is the Final Report and supersedes any preliminary report with this certificate number. Results apply to samples as submitted. All ages of this report have been checked and approved for release.

Signature:

Lawrence Ng, Laboratory Manager - Vancouver

ALS Chemex
EXCELLENCE IN ANALYTICAL CHEMISTRY
ALS Canada Ltd.
212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

STRATEGIC METALS LTD.
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO - RICH

Finalized Date: 13-NOV-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07128841

Sample Description	Method / Analyte / Units / LOR	ME-XRF05 Se ppm 2
C488408		NSS

Comments: NSS is non-sufficient sample.

ALS Chemex
EXCELLENCE IN ANALYTICAL CHEMISTRY
ALS Canada Ltd.
212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Finalized Date: 24-OCT-2007
Account: MTT

CERTIFICATE VA07117425

Project: NIMO

P.O. No.:

This report is for 1 Rock sample submitted to our lab in Vancouver, BC, Canada on 12-OCT-2007.

The following have access to data associated with this certificate:

AL ARCHER VANCOUVER OFFICE	DOUG EATON BILL WENGZYNOWSKI	JOAN MARIACHER

SAMPLE PREPARATION

ALS CODE	DESCRIPTION
FND-02	Find Sample for Addn Analysis

ANALYTICAL PROCEDURES

ALS CODE	DESCRIPTION	INSTRUMENT
ME-XRF05	Trace Level XRF Analysis	XRF

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

s is the Final Report and supersedes any preliminary report with this certificate number. Results apply to samples as submitted. All es of this report have been checked and approved for release.

Signature: Lawrence Ng

Lawrence Ng, Laboratory Manager - Vancouver

ALS Chemex
EXCELLENCE IN ANALYTICAL CHEMISTRY
ALS Canada Ltd.
212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO

Finalized Date: 24-OCT-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07117425

Sample Description	Method	ME-XRF05
	Analyte	Se
	Units	ppm
	LOR	2
C385636		4680

ALS Chemex
EXCELLENCE IN ANALYTICAL CHEMISTRY
ALS Canada Ltd.
212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Finalized Date: 24-OCT-2007
Account: MTT

CERTIFICATE VA07117424

Project: NIMO

P.O. No.:

This report is for 9 Rock samples submitted to our lab in Vancouver, BC, Canada on 12-OCT-2007.

The following have access to data associated with this certificate:

AL ARCHER VANCOUVER OFFICE	DOUG EATON BILL WENGZYNOWSKI	JOAN MARIACHER

SAMPLE PREPARATION

ALS CODE	DESCRIPTION
FND-02	Find Sample for Addn Analysis

ANALYTICAL PROCEDURES

ALS CODE	DESCRIPTION	INSTRUMENT
ME-XRF05	Trace Level XRF Analysis	XRF

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

This is the Final Report and supersedes any preliminary report with this certificate number. Results apply to samples as submitted. All pages of this report have been checked and approved for release.

Signature:

Lawrence Ng, Laboratory Manager - Vancouver

ALS Chemex
EXCELLENCE IN ANALYTICAL CHEMISTRY
ALS Canada Ltd.
212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO

Finalized Date: 24-OCT-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07117424

Sample Description	Method / Analyte / Units / LOR	ME-XRF05 Se ppm 2
C385601		2870
C385603		2930
C385605		2350
C385607		2090
C385609		2070
C385611		1985
C385616		2580
C385617		5990
C385633		1040

ALS Chemex
EXCELLENCE IN ANALYTICAL CHEMISTRY
ALS Canada Ltd.
212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Finalized Date: 15-OCT-2007
Account: MTT

CERTIFICATE VA07114509

Project: NIMO - RICH

P.O. No.: RI07-20

This report is for 1 Drill Core sample submitted to our lab in Vancouver, BC, Canada on 5-OCT-2007.

The following have access to data associated with this certificate:

AL ARCHER VANCOUVER OFFICE	DOUG EATON BILL WENGZYNOWSKI	JOAN MARIACHER

SAMPLE PREPARATION

ALS CODE	DESCRIPTION
FND-02	Find Sample for Addn Analysis

ANALYTICAL PROCEDURES

ALS CODE	DESCRIPTION	INSTRUMENT
PGM-ICP23	Pt, Pd, Au 30g FA ICP	ICP-AES

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

his is the Final Report and supersedes any preliminary report with this certificate number. Results apply to samples as submitted. All ages of this report have been checked and approved for release.

Signature:

Lawrence Ng, Laboratory Manager - Vancouver

ALS Chemex
EXCELLENCE IN ANALYTICAL CHEMISTRY
ALS Canada Ltd.
212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: STRATEGIC METALS LTD.
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO - RICH

Finalized Date: 15-OCT-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07114509

Sample Description	Method	PGM-ICP23	PGM-ICP23	PGM-ICP23
	Analyte	Au	Pt	Pd
	Units	ppm	ppm	ppm
	LOR	0.001	0.005	0.001
C488426		0.017	0.005	0.006

ALS Chemex
EXCELLENCE IN ANALYTICAL CHEMISTRY
ALS Canada Ltd.
212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: STRATEGIC METALS LTD.
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Finalized Date: 15-OCT-2007
Account: MTT

CERTIFICATE VA07114508

Project: NIMO - RICH

P.O. No.: R107-19

This report is for 3 Drill Core samples submitted to our lab in Vancouver, BC, Canada on 5-OCT-2007.

The following have access to data associated with this certificate:

AL ARCHER VANCOUVER OFFICE	DOUG EATON BILL WENGZYNOWSKI	JOAN MARIACHER

SAMPLE PREPARATION

ALS CODE	DESCRIPTION
FND-02	Find Sample for Addn Analysis

ANALYTICAL PROCEDURES

ALS CODE	DESCRIPTION	INSTRUMENT
PGM-ICP23	Pt, Pd, Au 30g FA ICP	ICP-AES

To: STRATEGIC METALS LTD.
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

is is the Final Report and supersedes any preliminary report with this certificate number. Results apply to samples as submitted. All ges of this report have been checked and approved for release.

Signature: Lawrence Ng

Lawrence Ng, Laboratory Manager - Vancouver

ALS Chemex
EXCELLENCE IN ANALYTICAL CHEMISTRY
ALS Canada Ltd.
212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: STRATEGIC METALS LTD.
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO - RICH

Finalized Date: 15-OCT-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07114508

Sample Description	Method	PGM-ICP23	PGM-ICP23	PGM-ICP23
	Analyte	Au	Pt	Pd
	Units	ppm	ppm	ppm
	LOR	0.001	0.005	0.001
C488394		0.004	0.005	0.002
C488395		0.009	<0.005	0.010
C488396		0.017	0.050	0.019

ALS Chemex
EXCELLENCE IN ANALYTICAL CHEMISTRY
ALS Canada Ltd.
212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Finalized Date: 14-OCT-2007
Account: MTT

CERTIFICATE VA07114507

Project: NIMO - RICH

P.O. No.: R107-18

This report is for 1 Drill Core sample submitted to our lab in Vancouver, BC, Canada on 5-OCT-2007.

The following have access to data associated with this certificate:

AL ARCHER VANCOUVER OFFICE	DOUG EATON BILL WENGZYNOWSKI	JOAN MARIACHER

SAMPLE PREPARATION

ALS CODE	DESCRIPTION
FND-02	Find Sample for Addn Analysis

ANALYTICAL PROCEDURES

ALS CODE	DESCRIPTION	INSTRUMENT
PGM-ICP23	Pt, Pd, Au 30g FA ICP	ICP-AES

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

This is the Final Report and supersedes any preliminary report with this certificate number. Results apply to samples as submitted. All pages of this report have been checked and approved for release.

Signature:

Lawrence Ng, Laboratory Manager - Vancouver

ALS Chemex
EXCELLENCE IN ANALYTICAL CHEMISTRY
ALS Canada Ltd.
212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO - RICH

Finalized Date: 14-OCT-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07114507

Sample Description	Method	PGM-ICP23	PGM-ICP23	PGM-ICP23
	Analyte	Au	Pt	Pd
	Units	ppm	ppm	ppm
	LOR	0.001	0.005	0.001
C488361		0.008	0.017	0.003

ALS Chemex
EXCELLENCE IN ANALYTICAL CHEMISTRY
ALS Canada Ltd.
212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Finalized Date: 14-OCT-2007
Account: MTT

CERTIFICATE VA07114506

Project: NIMO RICH

P.O. No.: RI07-17

This report is for 5 Drill Core samples submitted to our lab in Vancouver, BC, Canada on 5-OCT-2007.

The following have access to data associated with this certificate:

AL ARCHER VANCOUVER OFFICE	DOUG EATON BILL WENGZYNOWSKI	JOAN MARIACHER

SAMPLE PREPARATION

ALS CODE	DESCRIPTION
FND-02	Find Sample for Addn Analysis

ANALYTICAL PROCEDURES

ALS CODE	DESCRIPTION	INSTRUMENT
PGM-ICP23	Pt, Pd, Au 30g FA ICP	ICP-AES

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

This is the Final Report and supersedes any preliminary report with this certificate number. Results apply to samples as submitted. All pages of this report have been checked and approved for release.

Signature: Lawrence Ng, Laboratory Manager - Vancouver

ALS Chemex
EXCELLENCE IN ANALYTICAL CHEMISTRY
ALS Canada Ltd.
212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO RICH

Finalized Date: 14-OCT-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07114506

Sample Description	Method	PGM-ICP23	PGM-ICP23	PGM-ICP23
	Analyte	Au	Pt	Pd
	Units	ppm	ppm	ppm
	LOR	0.001	0.005	0.001
C488300		0.001	0.007	<0.001
C488301		<0.001	0.009	<0.001
C488302		0.003	0.016	0.003
C488303		0.002	<0.005	<0.001
C488305		0.002	0.007	<0.001

ALS Chemex
EXCELLENCE IN ANALYTICAL CHEMISTRY
ALS Canada Ltd.
212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Finalized Date: 18-OCT-2007
Account: MTT

CERTIFICATE VA07114505

Project: NIMO - RICH

P.O. No.: R107-16

This report is for 2 Drill Core samples submitted to our lab in Vancouver, BC, Canada on 5-OCT-2007.

The following have access to data associated with this certificate:

AL ARCHER VANCOUVER OFFICE	DOUG EATON BILL WENGZYNOWSKI	JOAN MARIACHER

SAMPLE PREPARATION

ALS CODE	DESCRIPTION
FND-02	Find Sample for Addn Analysis

ANALYTICAL PROCEDURES

ALS CODE	DESCRIPTION	INSTRUMENT
PGM-ICP23	Pt, Pd, Au 30g FA ICP	ICP-AES

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

This is the Final Report and supersedes any preliminary report with this certificate number. Results apply to samples as submitted. All pages of this report have been checked and approved for release.

Signature:

Lawrence Ng, Laboratory Manager - Vancouver

ALS Chemex
EXCELLENCE IN ANALYTICAL CHEMISTRY
ALS Canada Ltd.
212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO - RICH

Finalized Date: 18-OCT-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07114505

Sample Description	Method	PGM-ICP23	PGM-ICP23	PGM-ICP23
	Analyte	Au	Pt	Pd
	Units	ppm	ppm	ppm
	LOR	0.001	0.005	0.001
C488407		0.004	0.006	0.003
C488409		0.007	<0.005	0.003

ALS Chemex
EXCELLENCE IN ANALYTICAL CHEMISTRY
ALS Canada Ltd.
212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Finalized D...: 14-OCT-2007
Account: MTT

CERTIFICATE VA07114504

Project: NIMO RICH

P.O. No.: RI07-13

This report is for 1 Drill Core sample submitted to our lab in Vancouver, BC, Canada on 5-OCT-2007.

The following have access to data associated with this certificate:

AL ARCHER VANCOUVER OFFICE	DOUG EATON BILL WENGZYNOWSKI	JOAN MARIACHER

SAMPLE PREPARATION

ALS CODE	DESCRIPTION
FND-02	Find Sample for Addn Analysis

ANALYTICAL PROCEDURES

ALS CODE	DESCRIPTION	INSTRUMENT
PGM-ICP23	Pt, Pd, Au 30g FA ICP	ICP-AES

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

...is is the Final Report and supersedes any preliminary report with this certificate number. Results apply to samples as submitted. All ...ages of this report have been checked and approved for release.

Signature: Lawrence Ng, Laboratory Manager - Vancouver

ALS Chemex
EXCELLENCE IN ANALYTICAL CHEMISTRY
ALS Canada Ltd.
212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO RICH

Finalized Date: 14-OCT-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07114504

Sample Description	Method	PGM-ICP23	PGM-ICP23	PGM-ICP23
	Analyte	Au	Pt	Pd
	Units	ppm	ppm	ppm
	LOR	0.001	0.005	0.001
C488289		0.007	0.006	0.002

ALS Chemex
EXCELLENCE IN ANALYTICAL CHEMISTRY
ALS Canada Ltd.
212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Finalized D...: 14-OCT-2007
Account: MTT

CERTIFICATE VA07114503

Project: NIMO RICH

P.O. No.: R107-12

This report is for 3 Drill Core samples submitted to our lab in Vancouver, BC, Canada on 5-OCT-2007.

The following have access to data associated with this certificate:

AL ARCHER VANCOUVER OFFICE	DOUG EATON BILL WENGZYNOWSKI	JOAN MARIACHER

SAMPLE PREPARATION

ALS CODE	DESCRIPTION
FND-02	Find Sample for Addn Analysis

ANALYTICAL PROCEDURES

ALS CODE	DESCRIPTION	INSTRUMENT
PGM-ICP23	Pt, Pd, Au 30g FA ICP	ICP-AES

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

This is the Final Report and supersedes any preliminary report with this certificate number. Results apply to samples as submitted. All pages of this report have been checked and approved for release.

Signature:

Lawrence Ng, Laboratory Manager - Vancouver

ALS Chemex
EXCELLENCE IN ANALYTICAL CHEMISTRY
ALS Canada Ltd.
212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: STRATEGIC METALS LTD.
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Finalized Date: 14-OCT-2007
Account: MTT

Project: NIMO RICH

CERTIFICATE OF ANALYSIS VA07114503

Sample Description	Method Analyte Units LOR	PGM-ICP23 Au ppm 0.001	PGM-ICP23 Pt ppm 0.005	PGM-ICP23 Pd ppm 0.001
C488272		0.008	<0.005	<0.001
C488274		0.008	0.008	0.001
C488293		0.025	0.033	0.012

ALS Chemex
EXCELLENCE IN ANALYTICAL CHEMISTRY
ALS Canada Ltd.
212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Finalized Date: 14-OCT-2007
Account: MTT

CERTIFICATE VA07114502

Project: NIMO-RICH

P.O. No.: R107-10

This report is for 9 Drill Core samples submitted to our lab in Vancouver, BC, Canada on 5-OCT-2007.

The following have access to data associated with this certificate:

AL ARCHER VANCOUVER OFFICE	DOUG EATON BILL WENGZYNOWSKI	JOAN MARIACHER

SAMPLE PREPARATION

ALS CODE	DESCRIPTION
FND-02	Find Sample for Addn Analysis

ANALYTICAL PROCEDURES

ALS CODE	DESCRIPTION	INSTRUMENT
PGM-ICP23	Pt, Pd, Au 30g FA ICP	ICP-AES

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

s is the Final Report and supersedes any preliminary report with this certificate number. Results apply to samples as submitted. All ges of this report have been checked and approved for release.

Signature:

Lawrence Ng, Laboratory Manager - Vancouver

ALS Chemex
EXCELLENCE IN ANALYTICAL CHEMISTRY
ALS Canada Ltd.
212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO-RICH

Finalized Date: 14-OCT-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07114502

Sample Description	Method	PGM-ICP23	PGM-ICP23	PGM-ICP23
	Analyte	Au	Pt	Pd
	Units	ppm	ppm	ppm
	LOR	0.001	0.005	0.001
C488246		0.013	0.025	0.014
C488247		0.003	0.007	<0.001
C488248		0.008	0.007	<0.001
C488249		0.004	0.007	<0.001
C488250		0.005	0.016	0.005
C488251		0.002	<0.005	0.003
C488252		0.005	<0.005	0.003
C488253		0.006	0.005	0.002
C488256		0.007	0.010	0.002

ALS Chemex
EXCELLENCE IN ANALYTICAL CHEMISTRY
ALS Canada Ltd.
212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Finalized Da. . 21-OCT-2007
Account: MTT

CERTIFICATE VA07114501

Project: NIMO-RICH

P.O. No.: RI07-07

This report is for 14 Drill Core samples submitted to our lab in Vancouver, BC, Canada on 5-OCT-2007.

The following have access to data associated with this certificate:

AL ARCHER VANCOUVER OFFICE	DOUG EATON BILL WENGZYNOWSKI	JOAN MARIACHER

SAMPLE PREPARATION

ALS CODE	DESCRIPTION
FND-02	Find Sample for Addn Analysis

ANALYTICAL PROCEDURES

ALS CODE	DESCRIPTION	INSTRUMENT
PGM-ICP23	Pt, Pd, Au 30g FA ICP	ICP-AES

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

This is the Final Report and supersedes any preliminary report with this certificate number. Results apply to samples as submitted. All pages of this report have been checked and approved for release.

Signature:

Lawrence Ng, Laboratory Manager - Vancouver

ALS Chemex
EXCELLENCE IN ANALYTICAL CHEMISTRY
ALS Canada Ltd.
212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: STRATEGIC METALS LTD.
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Finalized Date: 21-OCT-2007
Account: MTT

Project: NIMO-RICH

CERTIFICATE OF ANALYSIS VA07114501

Sample Description	Method	PGM-ICP23	PGM-ICP23	PGM-ICP23
	Analyte	Au	Pt	Pd
	Units	ppm	ppm	ppm
	LOR	0.001	0.005	0.001
C385591		0.007	<0.005	<0.001
C385594		0.006	<0.005	0.001
C385595		0.004	<0.005	0.002
C385597		0.002	0.008	0.002
C385598		0.002	<0.005	0.003
C385599		0.001	0.006	0.003
C385600		0.001	<0.005	0.002
C488152		0.003	<0.005	0.002
C488153		<0.001	<0.005	0.002
C488154		<0.001	<0.005	0.003
C488155		0.001	<0.005	0.003
C488156		0.001	<0.005	<0.001
C488157		0.002	<0.005	0.003
C488160		0.002	<0.005	0.005

ALS Chemex
EXCELLENCE IN ANALYTICAL CHEMISTRY
ALS Canada Ltd.
212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

STRATEGIC METALS LTD.
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Finalized Date: 15-OCT-2007
This copy reported on 4-DEC-2007
Account: MTT

CERTIFICATE VA07114500

Project: NIMO RICH

P.O. No.: RI07-06

This report is for 13 Drill Core samples submitted to our lab in Vancouver, BC, Canada on 5-OCT-2007.

The following have access to data associated with this certificate:

AL ARCHER VANCOUVER OFFICE	DOUG EATON BILL WENGZYNOWSKI	JOAN MARIACHER

SAMPLE PREPARATION

ALS CODE	DESCRIPTION
FND-02	Find Sample for Addn Analysis

ANALYTICAL PROCEDURES

ALS CODE	DESCRIPTION	INSTRUMENT
PGM-ICP23	Pt, Pd, Au 30g FA ICP	ICP-AES

To: **STRATEGIC METALS LTD.**
ATTN: JOAN MARIACHER
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

This is the Final Report and supersedes any preliminary report with this certificate number. Results apply to samples as submitted. All pages of this report have been checked and approved for release.

Signature:

Lawrence Ng, Laboratory Manager - Vancouver

ALS Chemex
EXCELLENCE IN ANALYTICAL CHEMISTRY
ALS Canada Ltd.
212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

STRATEGIC METALS LTD.
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO RICH

Finalized Date: 15-OCT-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07114500

Sample Description	Method	PGM-ICP23	PGM-ICP23	PGM-ICP23
	Analyte	Au	Pt	Pd
	Units	ppm	ppm	ppm
	LOR	0.001	0.005	0.001
C488177		0.001	<0.005	0.004
C488179		0.006	0.013	0.005
C488182		0.007	0.012	0.002
C488183		<0.001	0.005	0.001
C488184		<0.001	<0.005	0.001
C488185		0.002	<0.005	<0.001
C488186		0.003	0.006	<0.001
C488187		<0.001	0.020	<0.001
C488188		<0.001	<0.005	<0.001
C488189		0.002	<0.005	0.002
C488190		0.001	0.007	0.001
C488191		0.005	<0.005	<0.001
C488194		0.006	0.008	0.002

ALS Chemex
EXCELLENCE IN ANALYTICAL CHEMISTRY
ALS Canada Ltd.
212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Finalized Date: 14-OCT-2007
Account: MTT

CERTIFICATE VA07114239

Project: NIMO RI

P.O. No.: RI07-05

This report is for 2 Drill Core samples submitted to our lab in Vancouver, BC, Canada on 5-OCT-2007.

The following have access to data associated with this certificate:

AL ARCHER VANCOUVER OFFICE	DOUG EATON BILL WENGZYNOWSKI	JOAN MARIACHER

SAMPLE PREPARATION

ALS CODE	DESCRIPTION
FND-02	Find Sample for Addn Analysis

ANALYTICAL PROCEDURES

ALS CODE	DESCRIPTION	INSTRUMENT
PGM-ICP23	Pt, Pd, Au 30g FA ICP	ICP-AES

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

This is the Final Report and supersedes any preliminary report with this certificate number. Results apply to samples as submitted. All pages of this report have been checked and approved for release.

Signature:

Lawrence Ng, Laboratory Manager - Vancouver

ALS Chemex
EXCELLENCE IN ANALYTICAL CHEMISTRY
ALS Canada Ltd.
212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO RI

Finalized Date: 14-OCT-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07114239

Sample Description	Method	PGM-ICP23	PGM-ICP23	PGM-ICP23
	Analyte	Au	Pt	Pd
	Units	ppm	ppm	ppm
	LOR	0.001	0.005	0.001
C385573		0.007	0.013	0.003
C385575		0.005	0.017	<0.001

ALS Chemex
EXCELLENCE IN ANALYTICAL CHEMISTRY
ALS Canada Ltd.
212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Finalized Date: 2-OCT-2007
Account: MTT

CERTIFICATE VA07100571

Project: NIMO RICH

P.O. No.: R107-12

This report is for 23 Drill Core samples submitted to our lab in Vancouver, BC, Canada on 15-AUG-2007.

The following have access to data associated with this certificate:

AL ARCHER VANCOUVER OFFICE	DOUG EATON BILL WENGZYNOWSKI	JOAN MARIACHER

SAMPLE PREPARATION

ALS CODE	DESCRIPTION
WEI-21	Received Sample Weight
LOG-22	Sample login - Rcd w/o BarCode
CRU-31	Fine crushing - 70% <2mm
SPL-21	Split sample - riffle splitter
PUL-31	Pulverize split to 85% <75 um

ANALYTICAL PROCEDURES

ALS CODE	DESCRIPTION	
ME-MS61	48 element four acid ICP-MS	
Hg-CV41	Trace Hg - cold vapor/AAS	FIMS

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

: is the Final Report and supersedes any preliminary report with this certificate number. Results apply to samples as submitted. All es of this report have been checked and approved for release.

Signature:

Lawrence Ng, Laboratory Manager - Vancouver

ALS Chemex

EXCELLENCE IN ANALYTICAL CHEMISTRY

ALS Canada Ltd.

212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: STRATEGIC METALS LTD.
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Finalized Date: 2-OCT-2007
Account: MTT

Project: NIMO RICH

CERTIFICATE OF ANALYSIS VA07100571

Sample Description	Method / Analyte / Units / LOR	WEI-21 Recvd Wt. kg 0.02	ME-MS61 Ag ppm 0.01	ME-MS61 Al % 0.01	ME-MS61 As ppm 0.2	ME-MS61 Ba ppm 10	ME-MS61 Be ppm 0.05	ME-MS61 Bi ppm 0.01	ME-MS61 Ca % 0.01	ME-MS61 Cd ppm 0.02	ME-MS61 Ce ppm 0.01	ME-MS61 Co ppm 0.1	ME-MS61 Cr ppm 1	ME-MS61 Cs ppm 0.05	ME-MS61 Cu ppm 0.2	ME-MS61 Fe % 0.01
C488264		2.54	0.61	2.07	17.9	920	1.24	0.05	0.09	12.3	15.55	4.5	42	2.73	51.9	1.1
C488265		2.46	0.33	1.31	14.3	1090	0.78	0.07	3.51	5.14	11.65	3.4	35	1.69	36.2	1.02
C488266		1.70	0.49	1.55	21.6	440	0.94	0.09	0.08	8.6	15.5	4.4	44	2.11	55.9	1.32
C488267		1.74	0.25	1.67	14.6	460	1.23	0.09	0.19	2.22	14.8	4.3	32	2.43	32.1	1.17
C488268		1.00	0.19	1.62	12.6	320	1.1	0.08	0.07	1.63	14.6	3.7	29	2.2	29	1.08
C488269		0.60	0.25	1.44	8.3	1250	0.84	0.08	0.04	1.57	10	2.6	36	1.79	23.3	0.89
C488270		0.86	0.14	1.36	10.7	630	0.97	0.07	0.04	1.24	10.75	3.2	34	1.77	24.3	1
C488271		0.96	0.17	1.3	13.2	620	0.9	0.07	0.04	2.14	12.5	3.1	26	1.6	25.5	0.93
C488272		0.20	0.22	1.75	19.2	310	1	0.08	0.06	3.02	13.3	4.7	31	1.94	41.2	1.2
C488274		0.66	0.48	6.99	75.9	820	3.29	0.23	5.88	3.02	44.8	18.3	88	9.92	64.4	4.12
C488275		0.72	0.17	2.45	20	760	1.33	0.07	27.7	1.42	18.9	4.3	32	2.87	20.4	1.14
C488276		1.18	0.19	0.1	6	120	0.09	6.05	20.2	0.09	1.42	1.1	1	0.22	3	0.46
C488277		0.96	0.1	0.98	10	1770	1.15	0.03	28.3	0.67	14.05	2	10	1.06	7.4	0.68
C488278		0.66	0.27	3.91	20	420	1.52	0.13	4.8	2.79	39.7	7.4	48	4.9	25.6	1.83
C488279		1.82	0.31	4.87	23.4	160	1.8	0.17	2.13	4.47	36.7	9.5	56	6.23	33	2.41
C488280		1.96	0.3	5.02	19.8	330	1.94	0.17	2.89	3.55	43.6	9.6	58	6.44	31.1	2.33
C488281		1.80	0.29	4.43	18.9	170	1.74	0.16	0.72	3.65	31.8	8.8	59	6.17	32.6	2.03
C488282		2.80	0.28	3.3	16.6	340	1.41	0.12	2.42	2.55	33.1	7.7	49	4.51	30.4	1.7
C488283		2.48	0.21	3.06	16.1	210	1.27	0.12	3.91	2.43	33	6.3	46	3.67	31.3	1.65
C488284		0.62	0.22	3.15	14.1	480	1.32	0.11	4.19	4.31	38.2	6.5	44	4.12	31.8	1.56
C488285		0.06	0.71	2.35	161.5	740	0.9	0.49	1.43	12.75	38.9	5.2	35	2.56	119.5	21
C488286		0.64	0.33	4.6	20.6	830	1.71	0.12	1.23	1.44	39.7	9.8	65	5.82	34.9	2.41
C488293		0.40	0.72	4.67	265	520	2.41	0.19	0.71	2.99	46.8	27.4	84	6.4	88	7.26

Comments: Interference: Ca>10% on ICP-MS As,ICP-AES results shown. REE's may not be totally soluble in MS61 method.

ALS Chemex

EXCELLENCE IN ANALYTICAL CHEMISTRY

ALS Canada Ltd.

212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO RICH

Finalized Date: 2-OCT-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07100571

Sample Description	Method	ME-MS61	ME-MS61	ME-MS61	Hg-CV41	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61
	Analyte	Ga	Ge	Hf	Hg	In	K	La	Li	Mg	Mn	Mo	Na	Nb	Ni	P
	Units	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	%	ppm	ppm	%	ppm	ppm	ppm
	LOR	0.05	0.05	0.1	0.01	0.005	0.01	0.5	0.2	0.01	5	0.05	0.01	0.1	0.2	10
C488264		5.96	0.13	0.6	0.13	0.021	0.63	10.4	5.1	0.15	40	39.7	0.04	3.5	123	210
C488265		3.6	0.09	0.6	0.09	0.012	0.4	8.4	3.6	0.34	82	43.9	0.05	2.8	117.5	400
C488266		4.59	0.12	0.8	0.12	0.018	0.49	11.4	4.3	0.11	53	44.5	0.04	3.2	164.5	210
C488267		4.53	0.11	0.8	0.08	0.015	0.52	9.5	4.5	0.19	65	46.1	0.03	3.3	169.5	160
C488268		4.12	0.09	0.7	0.06	0.012	0.51	9.5	4	0.11	45	37.9	0.04	3.1	132	180
C488269		3.55	0.08	0.7	0.06	0.009	0.44	5.9	4.3	0.09	44	32.4	0.04	2.8	96.5	90
C488270		3.21	0.08	0.6	0.05	0.01	0.39	6.3	4.3	0.09	40	46.1	0.04	2.7	137.5	90
C488271		3.7	0.11	0.6	0.07	0.011	0.37	7.3	5.7	0.08	42	36.9	0.03	2.4	133	140
C488272		5.9	0.16	0.8	0.11	0.017	0.48	7.5	10.1	0.12	58	41.8	0.04	3.4	179	210
C488274		23.3	0.49	2.5	0.23	0.059	2.1	25.3	11.4	0.56	211	83.5	0.08	11.2	395	720
C488275		6.91	0.17	0.8	0.08	0.024	0.75	12	3.9	0.4	259	19.3	0.04	3.6	62.3	210
C488276		0.41	0.22	<0.1	<0.01	0.008	0.03	0.9	0.9	12.7	191	0.57	0.01	0.3	3.5	260
C488277		2.69	0.16	0.4	0.03	0.009	0.29	9.7	2	2.78	240	7.08	0.02	1.7	24.5	270
C488278		9.86	0.15	1.6	0.10	0.035	1.21	23	6.7	0.44	119	31.6	0.05	6.4	113.5	200
C488279		12.55	0.16	1.8	0.12	0.046	1.5	21	7.7	0.95	178	32.5	0.07	7.7	121.5	260
C488280		13.8	0.15	2	0.11	0.042	1.56	24	6.9	0.42	97	28.3	0.11	8.1	101	300
C488281		12.2	0.13	1.8	0.11	0.04	1.37	17.5	6.6	0.35	73	35.3	0.06	6.8	126	160
C488282		9.12	0.15	1.5	0.09	0.031	1.02	19.7	5.4	0.6	124	36.8	0.07	5.9	129.5	200
C488283		7.75	0.13	1.5	0.07	0.024	0.92	20.1	4.6	0.36	101	38.2	0.08	5.3	127	350
C488284		8.23	0.13	1.6	0.10	0.031	0.96	23.1	4.4	0.45	117	50.3	0.12	5.8	123.5	310
C488285		6.2	0.63	1	0.33	0.026	0.7	25.2	2.5	0.18	66	34.4	0.12	3.9	157	450
C488286		12.1	0.12	2.4	0.10	0.04	1.39	22.8	5.9	0.34	78	51.2	0.16	8.3	152	260
C488293		19.75	1.16	1.8	0.15	0.051	1.42	39	12.5	0.34	143	264	0.04	8.1	3900	2960

Comments: Interference: Ca>10% on ICP-MS As,ICP-AES results shown. REE's may not be totally soluble in MS61 method.

ALS Chemex

EXCELLENCE IN ANALYTICAL CHEMISTRY

ALS Canada Ltd.

212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: STRATEGIC METALS LTD.
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Finalized Date: 2-OCT-2007
Account: MTT

Project: NIMO RICH

CERTIFICATE OF ANALYSIS VA07100571

Sample Description	Method	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61
	Analyte	Pb	Rb	Re	S	Sb	Sc	Se	Sn	Sr	Ta	Te	Th	Ti	Tl	U
	Units	ppm	ppm	ppm	%	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm
	LOR	0.5	0.1	0.002	0.01	0.05	0.1	1	0.2	0.2	0.05	0.05	0.2	0.005	0.02	0.1
C488264		7.1	42.4	0.049	1.08	20	4.3	17	0.8	31.4	0.22	0.14	2.4	0.097	2.73	6.8
C488265		4.3	25.4	0.051	0.82	12.7	2.9	12	0.5	200	0.14	0.12	1.8	0.063	2.53	6.6
C488266		5.2	32	0.053	1.12	15.35	3.9	15	0.7	30	0.18	0.18	2.1	0.08	4.16	7.4
C488267		5.2	34.9	0.052	0.98	6.63	4.1	11	0.7	38.6	0.18	0.12	2.1	0.08	2.65	7.7
C488268		5.6	32	0.041	0.92	4.78	3.6	10	0.6	29.6	0.19	0.1	2.1	0.076	2.2	7
C488269		4.8	26.1	0.034	0.66	3.59	3	9	0.5	31.2	0.16	0.06	1.7	0.071	1.65	5.8
C488270		4.7	24.6	0.042	0.83	3.07	3.2	10	0.5	38.8	0.15	0.09	1.6	0.062	2.15	7.5
C488271		3.9	22.9	0.037	0.79	3.49	2.9	16	0.5	44.1	0.14	0.07	1.6	0.062	2.46	6.1
C488272		5.3	30	0.047	1.05	5.44	3.7	27	0.6	39.6	0.2	0.08	2.2	0.084	3.42	7
C488274		14.6	142	0.202	3.99	17.2	11.4	93	2	176	0.66	0.39	6.4	0.305	10.85	13.9
C488275		4.9	47.1	0.02	1.32	5.54	3.7	18	0.8	898	0.2	0.06	2.5	0.101	2.69	2.9
C488276		4.9	1.8	0.002	0.04	0.14	0.5	2	<0.2	48.7	<0.05	<0.05	<0.2	<0.005	0.06	0.7
C488277		2	19.2	0.007	0.67	2.03	3.2	7	0.3	797	0.08	<0.05	1.2	0.041	1.07	1.5
C488278		8	76.8	0.031	1.98	5.46	7.8	12	1.3	147	0.42	0.06	5	0.188	3.55	6.1
C488279		10.2	94.6	0.027	2.47	6.94	9	14	1.7	108.5	0.48	0.08	5.6	0.232	4.53	5.3
C488280		11	99.4	0.022	2.44	6.03	9.6	10	1.7	89.6	0.53	0.05	6.1	0.243	4.27	4.7
C488281		9.7	91.3	0.03	2.05	4.99	8.6	9	1.5	55.8	0.44	0.08	5	0.206	4.65	5.1
C488282		8.6	70.5	0.035	1.76	4.21	7.5	9	1.3	113	0.37	0.07	4.5	0.172	4.14	6.4
C488283		7.7	59.2	0.038	1.77	3.96	6.4	9	1.1	170	0.34	0.09	4	0.157	3.7	6.8
C488284		7.3	61.7	0.037	1.7	3.06	6.7	7	1.2	178.5	0.36	0.07	4.5	0.166	3.65	8.3
C488285		51.6	40	<0.002	>10.0	14.9	4.2	84	1.5	121.5	0.22	0.19	3	0.126	7.11	6.4
C488286		11.6	85.6	0.035	2.56	4.01	8.9	10	1.6	91.4	0.52	0.1	6.1	0.249	4.87	8.7
C488293		16.2	92.1	2.57	8.02	32.6	9.3	282	1.5	129	0.48	1.66	4.6	0.212	27	19.1

Comments: Interference: Ca>10% on ICP-MS As,ICP-AES results shown. REE's may not be totally soluble in MS61 method.

ALS Chemex

EXCELLENCE IN ANALYTICAL CHEMISTRY

ALS Canada Ltd.

212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Finalized Date: 2-OCT-2007
Account: MTT

Project: NIMO RICH

CERTIFICATE OF ANALYSIS VA07100571

Sample Description	Method / Analyte / Units / LOR	ME-MS61 V ppm 1	ME-MS61 W ppm 0.1	ME-MS61 Y ppm 0.1	ME-MS61 Zn ppm 2	ME-MS61 Zr ppm 0.5
C488264		1030	0.4	11.9	1010	28.9
C488265		585	0.3	16.5	529	26.7
C488266		700	0.4	16.2	698	41.9
C488267		500	0.4	18.4	309	31.9
C488268		400	1.2	13.7	218	27.8
C488269		314	0.9	10.5	146	25.4
C488270		285	0.4	17.9	171	24.5
C488271		494	0.4	16.3	347	23
C488272		551	0.5	21.6	683	30.1
C488274		1080	1.1	43	946	82.2
C488275		388	0.3	32.1	205	25.1
C488276		10	0.1	1.2	21	0.7
C488277		172	0.2	39.2	73	17.2
C488278		512	0.7	28.8	224	53.8
C488279		732	0.9	15.9	365	60.9
C488280		640	0.8	25.1	290	64.2
C488281		674	0.8	12	294	55.8
C488282		594	0.7	16.8	196	54.3
C488283		655	0.6	26.5	176	51.7
C488284		395	0.7	22.9	371	56.3
C488285		261	1.4	9.9	974	35.3
C488286		502	1.1	16	119	74.5
C488293		1195	1.2	40.1	1030	62.1

Comments: Interference: Ca>10% on ICP-MS As,ICP-AES results shown. REE's may not be totally soluble in MS61 method.

ALS Chemex
EXCELLENCE IN ANALYTICAL CHEMISTRY
ALS Canada Ltd.
212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Finalized Date: 25-SEP-2007
Account: MTT

CERTIFICATE VA07100570

Project: NIMO RICH

P.O. No.: R1-07-08

This report is for 21 Drill Core samples submitted to our lab in Vancouver, BC, Canada on 15-AUG-2007.

The following have access to data associated with this certificate:

AL ARCHER VANCOUVER OFFICE	DOUG EATON BILL WENGZYNOWSKI	JOAN MARIACHER

SAMPLE PREPARATION

ALS CODE	DESCRIPTION
WEI-21	Received Sample Weight
CRU-31	Fine crushing - 70% <2mm
CRU-QC	Crushing QC Test
LOG-22	Sample login - Rcd w/o BarCode
SPL-21	Split sample - riffle splitter
PUL-32	Pulverize 1000g to 85% < 75 um

ANALYTICAL PROCEDURES

ALS CODE	DESCRIPTION	
ME-MS61	48 element four acid ICP-MS	
Hg-CV41	Trace Hg - cold vapor/AAS	FIMS

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

is the Final Report and supersedes any preliminary report with this certificate number. Results apply to samples as submitted. All es of this report have been checked and approved for release.

Signature: Lawrence Ng

Lawrence Ng, Laboratory Manager - Vancouver

ALS Chemex
EXCELLENCE IN ANALYTICAL CHEMISTRY
ALS Canada Ltd.
212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: STRATEGIC METALS LTD.
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO RICH

Finalized Date: 25-SEP-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07100570

Sample Description	Method	WEI-21	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61
	Analyte	Recvd Wt.	Ag	Al	As	Ba	Be	Bi	Ca	Cd	Ce	Co	Cr	Cs	Cu	Fe
	Units	kg	ppm	%	ppm	ppm	ppm	ppm	%	ppm	ppm	ppm	ppm	ppm	ppm	%
	LOR	0.02	0.01	0.01	0.2	10	0.05	0.01	0.01	0.02	0.01	0.1	1	0.05	0.2	0.01
C488201		1.26	0.42	1.38	13.8	1280	0.93	0.04	0.06	10.25	9.82	3.1	55	1.52	53.3	1.06
C488202		1.00	0.52	1.86	27.1	650	1.2	0.06	0.19	4.95	18.45	5.3	45	1.89	52.8	1.84
C488203		1.42	0.2	1.78	11.5	670	1.12	0.04	0.14	2.72	11.45	3.8	46	1.68	27.1	1.13
C488204		1.32	0.14	1.56	10.3	980	0.97	0.04	0.07	3.1	13.65	3.7	32	1.44	28.7	1.08
C488205		1.24	0.17	1.87	13.7	700	1.16	0.05	0.05	4.03	14.45	4.3	47	1.59	36.2	1.18
C488206		0.76	0.12	1.53	13.6	710	0.93	0.04	0.05	3.8	13.4	3.8	33	1.4	29.7	1.17
C488207		0.86	0.21	2.09	27.3	690	1.17	0.07	0.05	2.12	18.5	5.9	37	1.81	45.9	1.73
C488208		0.52	0.19	1.59	14.8	750	1.05	0.06	0.04	3.07	12.85	3.9	31	1.72	27.3	1.1
C488209		0.56	0.26	2.01	23.1	620	1.22	0.05	0.04	3.36	15.55	4.4	41	1.97	39.7	1.26
C488234		0.42	0.3	5.23	42.8	650	2.12	0.13	1.04	3.54	35	9.6	73	6.41	43.6	2.63
C488235		0.62	0.29	6.44	47.4	840	2.69	0.17	3.89	3.38	62.8	11.6	68	7.79	46	2.86
C488236		0.86	0.26	3.69	22.1	670	1.41	0.09	4.89	2.89	32.3	6.7	57	4.56	28	2.05
C488237		0.84	0.25	4.16	19.1	780	1.49	0.09	1.54	3.74	30.1	7.7	56	4.95	27.4	1.85
C488238		1.90	0.29	5.41	21.2	720	1.86	0.13	3.83	3.36	40	9.7	66	6.38	31.1	2.39
C488239		1.78	0.28	5.05	20.7	630	1.8	0.14	1.52	3.66	34.4	9.4	65	6.15	34.4	2.38
C488240		1.76	0.28	4.14	18.8	600	1.48	0.31	2.94	2.77	34.1	8.2	60	4.76	30.5	1.95
C488241		2.40	0.23	3.18	16.1	780	1.38	0.08	3.24	2.91	30	6.8	51	3.66	33.2	1.72
C488242		2.64	0.2	2.96	14.6	810	1.14	0.07	3.37	2.41	27.5	5.9	47	3.3	30.7	1.44
C488243		0.56	0.21	4.56	14.3	880	1.58	0.1	4.6	0.87	51.7	9.7	58	4.9	28.5	1.79
C488244		0.04	0.63	3.45	88.1	950	0.78	0.11	0.84	1.23	28.5	7.2	45	3.3	80.5	24.4
C488245		0.58	0.31	6.27	21.6	1050	2.34	0.15	0.99	3.73	48.4	12.6	85	7.46	40.1	2.66

Comments: REE's may not be totally soluble in MS61 method.

ALS Chemex
EXCELLENCE IN ANALYTICAL CHEMISTRY
ALS Canada Ltd.
212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO RICH

Finalized Date: 25-SEP-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07100570

Sample Description	Method	ME-MS61	ME-MS61	ME-MS61	Hg-CV41	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61
	Analyte	Ga	Ge	Hf	Hg	In	K	La	Li	Mg	Mn	Mo	Na	Nb	Ni	P
	Units	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	%	ppm	ppm	%	ppm	ppm	ppm
	LOR	0.05	0.05	0.1	0.01	0.005	0.01	0.5	0.2	0.01	5	0.05	0.01	0.1	0.2	10
C488201		3.68	0.1	0.4	0.09	0.015	0.4	6.4	6.4	0.09	43	39.2	0.03	2.3	137	180
C488202		4.62	0.13	0.5	0.11	0.012	0.56	13.9	6.5	0.14	68	35.7	0.03	3.3	179.5	410
C488203		3.79	0.09	0.4	0.07	0.011	0.5	7.4	9.2	0.14	56	35.3	0.03	2.8	163.5	200
C488204		3.34	0.11	0.4	0.07	0.009	0.42	8.6	16.8	0.07	49	38	0.03	2.7	175	350
C488205		4.08	0.11	0.5	0.08	0.011	0.52	9.2	13.9	0.09	44	60.3	0.03	3.5	201	290
C488206		3.22	0.1	0.4	0.07	0.008	0.41	8.7	10.8	0.08	53	47	0.03	2.9	158.5	290
C488207		4.59	0.16	0.7	0.15	0.01	0.56	11.2	12.9	0.12	53	70.6	0.03	3.9	246	270
C488208		3.83	0.12	0.5	0.07	0.012	0.39	7	7.1	0.09	55	36	0.03	2.8	184	170
C488209		6.12	0.16	0.6	0.10	0.013	0.53	8.7	6	0.12	47	48.2	0.03	3.4	253	250
C488234		14.6	0.24	1.6	0.17	0.038	1.57	21.1	8.8	0.41	107	36.3	0.07	7.8	152	250
C488235		19.3	0.33	2	0.18	0.041	1.89	38.6	9.8	0.55	130	33.2	0.08	10.2	177.5	1110
C488236		9.36	0.17	1.1	0.12	0.03	1.08	18.8	9.1	1.06	196	26.8	0.06	5.7	88.8	130
C488237		10.45	0.15	1.3	0.14	0.029	1.28	18.3	6.8	0.34	94	25.3	0.08	6.1	94.1	240
C488238		13.7	0.15	1.7	0.13	0.035	1.61	22.6	7.3	0.57	130	27.8	0.12	8.1	99.7	290
C488239		12.85	0.15	1.5	0.13	0.037	1.53	19.5	6.9	0.44	91	32.3	0.09	7.2	119.5	200
C488240		10.25	0.15	1.4	0.12	0.034	1.21	20.7	5.5	0.42	95	35.6	0.1	6.3	130	240
C488241		8.07	0.14	1.2	0.09	0.026	0.94	18.8	4.9	0.71	146	38.2	0.11	5.4	136.5	250
C488242		7.11	0.12	1	0.08	0.02	0.87	17.9	3.9	0.33	86	36.6	0.05	4.8	132.5	260
C488243		11.75	0.16	2.1	0.08	0.033	1.41	28.9	6.1	0.36	109	31.6	0.21	8.9	98.9	760
C488244		8.05	0.68	1.4	0.22	0.015	1	15.2	3.2	0.22	79	19.15	0.21	6.2	87.2	220
C488245		16.4	0.15	2.6	0.15	0.049	1.93	26.7	8	0.44	93	38.7	0.16	10.8	138	350

Comments: REE's may not be totally soluble in MS61 method.

ALS Chemex

EXCELLENCE IN ANALYTICAL CHEMISTRY

ALS Canada Ltd.

212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Finalized Date: 25-SEP-2007
Account: MTT

Project: NIMO RICH

CERTIFICATE OF ANALYSIS VA07100570

Sample Description	Method	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61
	Analyte	Pb	Rb	Re	S	Sb	Sc	Se	Sn	Sr	Ta	Te	Th	Ti	Tl	U
	Units	ppm	ppm	ppm	%	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm
	LOR	0.5	0.1	0.002	0.01	0.05	0.1	1	0.2	0.2	0.05	0.05	0.2	0.005	0.02	0.1
C488201		4.2	22.6	0.041	0.89	15.55	3	13	0.5	24.2	0.14	0.11	1.6	0.067	3.34	5.4
C488202		6	31.7	0.042	1.67	15.4	4	17	0.6	40.2	0.19	0.17	1.9	0.09	4.21	5.8
C488203		4.5	27.3	0.037	0.97	5.29	3.5	10	0.6	40.8	0.16	0.09	1.7	0.078	2.2	6
C488204		4.8	24.4	0.034	0.87	3.73	3.4	10	0.7	54	0.16	0.07	1.8	0.062	2.11	7
C488205		6.3	28.9	0.051	1.1	3.64	4.2	12	0.6	50.4	0.2	0.12	1.9	0.08	3.07	9.1
C488206		4.8	22.9	0.037	0.96	2.81	3.3	13	0.5	59.8	0.16	0.08	1.7	0.072	2.66	7.1
C488207		7.8	32	0.054	1.69	5.04	4.6	20	0.6	43.4	0.23	0.12	2.2	0.1	5.33	9.9
C488208		4.1	25.7	0.037	0.93	3.15	3.3	14	0.6	21.1	0.17	0.07	1.8	0.072	2.46	5.6
C488209		5.3	31.3	0.05	1.32	4.24	3.9	22	0.6	29.4	0.22	0.11	2.2	0.098	3.89	7.4
C488234		11.7	97.8	0.036	2.68	8.71	9.1	39	1.5	79.8	0.5	0.1	5.9	0.259	5.35	6.1
C488235		13.1	122	0.024	3.06	9.26	12	53	1.7	155	0.64	0.2	7.4	0.312	5.33	7.5
C488236		8.4	67.8	0.025	2.16	6.17	7.2	17	1.2	164	0.36	0.05	4.2	0.172	3.46	4.4
C488237		9	76.5	0.023	1.88	5.4	7.6	13	1.4	95.2	0.42	0.06	4.9	0.206	3.62	4.2
C488238		11	99	0.019	2.55	5.86	9.8	14	1.7	117	0.53	0.06	6	0.259	4.02	4.6
C488239		10.4	92.2	0.025	2.47	5.22	9.6	12	1.6	71.1	0.47	0.06	5.4	0.236	4.34	4.7
C488240		9	73.5	0.033	2.12	4.64	8.3	12	1.4	111	0.42	0.07	5	0.207	4.66	5.9
C488241		7.8	56.2	0.041	1.86	4.16	6.7	11	1.2	140	0.33	0.08	4.2	0.168	3.75	6.5
C488242		6.7	52	0.032	1.6	3.61	6.1	8	1	160	0.3	0.08	3.7	0.148	3.23	5.8
C488243		9.5	81.3	0.023	1.9	2.99	9.1	8	1.6	184.5	0.57	0.06	6.8	0.272	3.08	6.9
C488244		44.8	56.3	0.01	>10.0	14.65	5	86	1.4	95.5	0.39	0.12	4.3	0.203	6.24	4.2
C488245		13.4	116	0.028	2.7	4.63	11.6	10	2.1	79.9	0.69	0.09	8.4	0.361	4.68	7.5

Comments: REE's may not be totally soluble in MS61 method.

ALS Chemex

EXCELLENCE IN ANALYTICAL CHEMISTRY

ALS Canada Ltd.

212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO RICH

Finalized Date: 25-SEP-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07100570

Sample Description	Method	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61
	Analyte	V	W	Y	Zn	Zr
	Units	ppm	ppm	ppm	ppm	ppm
	LOR	1	0.1	0.1	2	0.5
C488201		695	0.3	12.1	826	22.8
C488202		568	0.7	21.4	477	29.9
C488203		412	0.4	12.9	299	23.7
C488204		308	0.3	11.9	252	22.2
C488205		303	0.4	13.1	207	28
C488206		172	0.4	8	158	23.2
C488207		327	0.5	15.5	229	32.5
C488208		549	0.3	14.5	437	23.6
C488209		792	0.4	21.6	564	30.4
C488234		848	0.8	14.5	483	56.6
C488235		858	1	38.4	476	69.7
C488236		520	0.6	18.7	256	42.6
C488237		593	0.7	10.9	339	47.4
C488238		626	0.9	25.4	302	57
C488239		671	0.8	13.4	336	52.1
C488240		681	0.8	17.3	244	50.6
C488241		636	0.6	19.7	234	45.6
C488242		641	0.6	18.4	209	39.7
C488243		402	1	27.6	69	70.7
C488244		381	0.7	9.4	25	48.8
C488245		779	1.2	13.4	357	86.6

Comments: REE's may not be totally soluble in MS61 method.

ALS Chemex
EXCELLENCE IN ANALYTICAL CHEMISTRY
ALS Canada Ltd.
212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Finalized Date: 1-OCT-2007
Account: MTT

CERTIFICATE VA07099398

Project: NIMO - RICH

P.O. No.: R107-20

This report is for 22 Drill Core samples submitted to our lab in Vancouver, BC, Canada on 31-AUG-2007.

The following have access to data associated with this certificate:

AL ARCHER VANCOUVER OFFICE	DOUG EATON BILL WENGZYNOWSKI	JOAN MARIACHER

SAMPLE PREPARATION

ALS CODE	DESCRIPTION
WEI-21	Received Sample Weight
LOG-22	Sample login - Rcd w/o BarCode
CRU-31	Fine crushing - 70% <2mm
SPL-21	Split sample - riffle splitter
PUL-31	Pulverize split to 85% <75 um

ANALYTICAL PROCEDURES

ALS CODE	DESCRIPTION	
ME-MS61	48 element four acid ICP-MS	
Hg-CV41	Trace Hg - cold vapor/AAS	FIMS

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

This is the Final Report and supersedes any preliminary report with this certificate number. Results apply to samples as submitted. All pages of this report have been checked and approved for release.

Signature:

Lawrence Ng, Laboratory Manager - Vancouver

ALS Chemex

EXCELLENCE IN ANALYTICAL CHEMISTRY

ALS Canada Ltd.

212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO - RICH

Finalized Date: 1-OCT-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07099398

Sample Description	Method	WEI-21	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61
	Analyte	Recvd Wt.	Ag	Al	As	Ba	Be	Bi	Ca	Cd	Ce	Co	Cr	Cs	Cu	Fe
	Units	kg	ppm	%	ppm	ppm	ppm	ppm	%	ppm	ppm	ppm	ppm	ppm	ppm	%
	LOR	0.02	0.01	0.01	0.2	10	0.05	0.01	0.01	0.02	0.01	0.1	1	0.05	0.2	0.01
C488415		2.42	0.2	2.55	26	120	1.28	0.16	0.27	0.99	21.1	11.3	31	2.11	36	3.1
C488416		2.04	0.26	2.63	20.4	110	1.44	0.21	0.83	1.45	26.7	14.6	31	2.33	48.2	3.05
C488417		1.42	0.34	3	32.3	130	1.72	0.24	0.34	1.36	30.2	17.3	36	2.88	57.4	3.77
C488418		1.92	0.38	4.59	35.2	100	2.87	0.46	0.49	1.5	45.4	27	55	4.72	81.6	4.93
C488419		1.64	0.32	3.99	51.1	180	1.99	0.31	3.58	1.3	37.8	18.9	42	3.8	59.8	4.33
C488420		0.82	0.35	4.28	66.3	140	2.17	0.27	0.6	1.61	34.1	17.9	52	4.3	62	4.61
C488421		0.34	0.06	0.76	<5	500	0.61	<0.01	13.4	0.67	13.9	3.5	13	0.65	8.8	1.35
C488422		1.20	0.03	0.12	<5	20	0.06	<0.01	21.4	0.07	1.37	1.3	2	0.15	1.7	0.44
C488423		0.46	0.17	2.03	21.2	100	1.04	0.12	2.67	0.67	18.25	7.4	24	2.1	26.9	2.17
C488424		0.58	0.31	4.16	47.4	130	1.95	0.15	0.49	1.19	29.1	14.2	45	3.98	51.7	4.09
C488425		0.59	0.42	6.48	62.9	170	2.85	0.16	1.68	1.55	108	18.6	38	4.69	59.2	6.08
C488426		0.17	0.34	3.38	124	60	1.53	0.16	0.92	1.92	40.4	16.6	42	3.04	45.8	5.59
C488427		0.57	0.25	2.69	33.3	100	1.35	0.09	0.75	0.86	19.85	9.9	30	2.48	36.2	3.27
C488428		0.59	0.32	4.09	35.7	140	1.84	0.11	0.79	1.83	28.7	10.7	28	2.7	36.8	3.65
C488429		0.73	0.26	1.92	21.2	90	1.1	0.07	0.68	1.98	15.75	7.9	33	1.96	29.4	2.61
C488430		0.92	0.28	2.14	22.5	100	1.28	0.08	0.61	1.37	20.4	8	36	1.92	32.2	2.44
C488431		1.51	0.28	2.29	23.1	140	1.3	0.08	0.3	1.97	16.95	8.1	35	1.77	34.5	2.1
C488432		1.28	0.29	2.15	19.5	150	1.35	0.1	0.43	2.02	20.7	8.1	35	1.94	40.8	2.24
C488433		1.94	0.3	1.95	18.7	130	1.11	0.08	0.39	1.77	19.05	7.3	35	1.83	39	2.35
C488434		2.07	0.3	1.97	18	100	1.09	0.09	0.71	1.21	19.4	7.4	34	1.7	39.6	2.46
C488435		0.18	0.14	0.95	9	110	0.62	0.02	12.05	0.85	35.1	5.7	16	0.75	16.7	2.24
C488436		2.47	0.32	2.11	21.5	90	1.27	0.09	1.09	2.19	21.6	8.6	38	1.91	42.6	2.53

Comments: Interference: Ca>10% on ICP-MS As,ICP-AES results shown. REE's may not be totally soluble in MS61 method.

ALS Chemex

EXCELLENCE IN ANALYTICAL CHEMISTRY

ALS Canada Ltd.

212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO - RICH

Finalized Date: 1-OCT-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07099398

Sample Description	Method	ME-MS61	ME-MS61	ME-MS61	Hg-CV41	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61
	Analyte	Ga	Ge	Hf	Hg	In	K	La	Li	Mg	Mn	Mo	Na	Nb	Ni	P
	Units	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	%	ppm	ppm	%	ppm	ppm	ppm
	LOR	0.05	0.05	0.1	0.01	0.005	0.01	0.5	0.2	0.01	5	0.05	0.01	0.1	0.2	10
C488415		6.49	0.11	1.5	0.18	0.041	0.74	9.8	5.2	0.19	89	29.3	0.03	4.9	98.4	360
C488416		7.22	0.13	1.3	0.21	0.051	0.78	11.7	6.3	0.52	138	18.95	0.03	4.5	83.8	320
C488417		9.11	0.15	1.7	0.28	0.066	0.94	13.7	6.1	0.31	91	36.9	0.03	5.8	105	270
C488418		14.7	0.19	2.5	0.38	0.095	1.55	19.2	10.4	0.49	167	20.2	0.04	9	94.5	340
C488419		11.35	0.16	2.5	0.36	0.068	1.28	17.5	7.2	0.56	173	36.6	0.04	8	110	570
C488420		12.55	0.17	2.6	0.44	0.071	1.38	15	8.2	0.49	146	49.2	0.04	6.4	138	360
C488421		2.12	0.09	0.7	0.07	0.014	0.22	5.7	2.6	6.9	599	7.34	0.02	1.7	31.9	240
C488422		0.36	0.06	<0.1	<0.01	0.005	0.03	0.6	1.2	13.25	201	0.31	0.01	0.4	3.2	240
C488423		5.78	0.1	1.5	0.19	0.028	0.6	8.9	4.8	1.47	196	22.2	0.03	4.7	74.2	170
C488424		12.2	0.15	2.9	0.37	0.062	1.3	13.2	7.1	0.4	114	51.8	0.03	9	148.5	460
C488425		15.5	0.31	4.1	0.38	0.068	1.79	55.2	10.2	0.56	392	73.2	0.04	24	216	2360
C488426		8.6	0.26	3.1	0.26	0.083	1.09	15.9	7	0.22	128	129.5	0.03	25.8	795	2920
C488427		7.36	0.13	2.1	0.23	0.035	0.8	9.1	6.4	0.44	129	38.9	0.03	6.1	141.5	310
C488428		9.31	0.16	2.7	0.27	0.03	1.11	13.1	8.2	0.23	222	43.7	0.03	7.1	166.5	530
C488429		5.3	0.11	1.4	0.15	0.033	0.58	7.7	5.5	0.34	129	37.6	0.03	4	125	180
C488430		5.87	0.11	1.6	0.16	0.028	0.63	10	6.5	0.34	110	37.6	0.03	5.3	136	300
C488431		5.34	0.11	1.1	0.13	0.024	0.56	8.2	9	0.12	52	35.8	0.03	3.9	190	350
C488432		6.05	0.12	1.1	0.12	0.029	0.62	11.3	7.1	0.23	96	33.4	0.02	4	144.5	330
C488433		5.81	0.12	1	0.13	0.022	0.59	10.3	7.5	0.21	84	41.3	0.02	3.7	125.5	240
C488434		5.86	0.13	1	0.15	0.023	0.6	10.1	7.8	0.29	98	44	0.02	3.6	149	270
C488435		2.86	0.14	0.6	0.07	0.015	0.27	15.3	4.8	4.56	593	27.7	0.02	1.8	106.5	260
C488436		6.22	0.13	1	0.16	0.027	0.64	11.3	7.4	0.51	115	54.3	0.02	3.9	154.5	310

Comments: Interference: Ca>10% on ICP-MS As,ICP-AES results shown. REE's may not be totally soluble in MS61 method.

ALS Chemex

EXCELLENCE IN ANALYTICAL CHEMISTRY

ALS Canada Ltd.

212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO - RICH

Finalized Date: 1-OCT-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07099398

Sample Description	Method	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61
	Analyte	Pb	Rb	Re	S	Sb	Sc	Se	Sn	Sr	Ta	Te	Th	Ti	Tl	U
	Units	ppm	ppm	ppm	%	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm
	LOR	0.5	0.1	0.002	0.01	0.05	0.1	1	0.2	0.2	0.05	0.05	0.2	0.005	0.02	0.1
C488415		10.4	39.2	0.039	3.41	0.94	6.4	5	1	50.7	0.33	0.14	3.2	0.128	2.51	8.5
C488416		10.2	41.8	0.024	3.44	1.02	7.7	5	1	72	0.29	0.18	3.3	0.125	2.77	5.9
C488417		12.2	50.6	0.036	4.41	1.34	7.9	6	1.2	42.3	0.37	0.21	3.6	0.153	4.15	9.9
C488418		19.3	82.8	0.022	5.74	2.01	13	8	1.7	51.2	0.57	0.36	5.7	0.236	4.74	9.1
C488419		13.7	66.4	0.038	5.18	2.07	10.6	7	1.5	119.5	0.49	0.25	5.2	0.2	4.38	9.2
C488420		14	74	0.047	5.47	2.52	11.2	8	1.6	52.2	0.51	0.23	5.2	0.225	5.22	10.2
C488421		2.1	11.9	0.006	1.45	0.38	5.1	2	0.3	858	0.09	<0.05	1	0.037	0.72	5
C488422		1.5	1.4	<0.002	0.04	<0.05	0.5	<1	<0.2	47.6	<0.05	<0.05	0.2	<0.005	0.03	1.3
C488423		6.6	36.7	0.017	2.76	1.07	5.1	3	0.8	147.5	0.24	0.08	2.8	0.106	2.3	5
C488424		12.3	73.4	0.049	4.9	2.32	11.7	7	1.5	48	0.47	0.14	5	0.222	4.69	11.5
C488425		13.9	91.4	0.102	7.07	3.93	19.1	12	1.7	150.5	1.81	0.22	6.2	0.339	5.08	16
C488426		8.7	53.3	0.474	6.62	4.2	9.1	20	1.2	73.5	0.4	0.31	3.9	0.198	6.6	16.7
C488427		8.7	45.4	0.042	3.74	2.04	8.9	6	1	56.6	0.31	0.11	2.9	0.135	3.57	7.3
C488428		9.5	55.3	0.058	4.63	2.86	9.4	8	1	48.3	0.37	0.13	3.6	0.169	3.97	9.9
C488429		6.8	33.4	0.037	2.65	2.03	5.8	6	0.8	53.9	0.25	0.1	2.3	0.097	2.81	7.4
C488430		7.4	35.1	0.035	2.68	2.29	6.4	6	0.8	57.7	0.39	0.12	2.8	0.11	2.87	7.6
C488431		7	32.1	0.027	2.61	2.31	6.3	6	0.7	35.6	0.23	0.09	2.5	0.099	2.93	7.1
C488432		7.5	36.2	0.024	2.33	2.64	6.3	6	0.8	47.1	0.25	0.13	3	0.109	2.84	5.8
C488433		8.4	33.5	0.03	2.45	2.24	5.5	5	0.7	42.7	0.22	0.12	2.6	0.097	2.84	6.7
C488434		8.6	33.1	0.03	2.67	1.89	5.6	6	0.7	54.4	0.23	0.13	2.5	0.097	3.05	6.8
C488435		3.7	14.8	0.016	2.47	1.14	18.4	5	0.3	755	0.12	0.06	1.2	0.042	1.46	6.7
C488436		9	36.6	0.034	2.92	2.31	6.5	6	0.8	76.9	0.24	0.12	2.7	0.103	3.48	9.9

Comments: Interference: Ca>10% on ICP-MS As,ICP-AES results shown. REE's may not be totally soluble in MS61 method.

ALS Chemex
EXCELLENCE IN ANALYTICAL CHEMISTRY
ALS Canada Ltd.
212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO - RICH

Finalized Date: 1-OCT-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07099398

Sample Description	Method	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61
	Analyte	V	W	Y	Zn	Zr
	Units	ppm	ppm	ppm	ppm	ppm
	LOR	1	0.1	0.1	2	0.5
C488415		98	0.8	14.6	171	46
C488416		88	0.8	21	235	42.8
C488417		101	1.1	18.5	177	52.8
C488418		131	1.3	30.3	193	83.3
C488419		126	1.1	27.4	212	77.1
C488420		165	1.1	24.2	224	83.3
C488421		43	0.3	38.1	156	30.1
C488422		3	0.1	1	18	0.9
C488423		103	0.5	14.9	100	45.9
C488424		242	0.9	18.9	164	88.1
C488425		284	1.1	46.9	346	122
C488426		381	1	70.3	439	136.5
C488427		211	0.5	20.8	218	60.3
C488428		345	0.6	19.8	425	76.1
C488429		350	0.5	20	481	45.4
C488430		351	0.5	17.5	369	50.3
C488431		352	0.5	16.5	331	39
C488432		344	0.5	18.2	413	37.6
C488433		266	0.6	16.1	321	34.2
C488434		223	0.5	15.8	265	33.3
C488435		165	0.4	72.8	215	24.5
C488436		268	0.6	19.2	308	37.3

Comments: Interference: Ca>10% on ICP-MS As,ICP-AES results shown. REE's may not be totally soluble in MS61 method.

ALS Chemex
EXCELLENCE IN ANALYTICAL CHEMISTRY
ALS Canada Ltd.
212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Finalized . .e: 9-OCT-2007
Account: MTT

CERTIFICATE VA07099397

Project: NIMO - RICH

P.O. No.: R107-22

This report is for 14 Drill Core samples submitted to our lab in Vancouver, BC, Canada on 31-AUG-2007.

The following have access to data associated with this certificate:

AL ARCHER VANCOUVER OFFICE	DOUG EATON BILL WENGZYNOWSKI	JOAN MARIACHER

SAMPLE PREPARATION

ALS CODE	DESCRIPTION
WEI-21	Received Sample Weight
LOG-22	Sample login - Rcd w/o BarCode
CRU-31	Fine crushing - 70% <2mm
SPL-21	Split sample - riffle splitter
PUL-31	Pulverize split to 85% <75 um

ANALYTICAL PROCEDURES

ALS CODE	DESCRIPTION	
ME-MS61	48 element four acid ICP-MS	
Hg-CV41	Trace Hg - cold vapor/AAS	FIMS

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

his is the Final Report and supersedes any preliminary report with this certificate number. Results apply to samples as submitted. All ges of this report have been checked and approved for release.

Signature: Lawrence Ng

Lawrence Ng, Laboratory Manager - Vancouver

ALS Chemex
EXCELLENCE IN ANALYTICAL CHEMISTRY
ALS Canada Ltd.
212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO - RICH

Finalized Date: 9-OCT-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07099397

Sample Description	Method	WEI-21	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61
	Analyte	Recvd Wt.	Ag	Al	As	Ba	Be	Bi	Ca	Cd	Ce	Co	Cr	Cs	Cu	Fe
	Units	kg	ppm	%	ppm	ppm	ppm	ppm	%	ppm	ppm	ppm	ppm	ppm	ppm	%
	LOR	0.02	0.01	0.01	0.2	10	0.05	0.01	0.01	0.02	0.01	0.1	1	0.05	0.2	0.01
C488437		2.40	0.29	3.26	33.7	140	1.69	0.26	0.26	6.48	27.6	17.4	45	3.59	55.5	3.81
C488438		2.27	0.21	3.22	36.8	120	1.56	0.18	0.87	6.38	27.9	15.2	43	2.81	38.9	4.02
C488439		1.65	0.31	3.72	76.9	100	1.74	0.24	0.47	6.67	26.5	23.1	44	3.43	53.3	5.87
C488440		1.37	0.25	3.37	58.6	100	1.73	0.2	0.44	5.28	23.5	17.7	40	3.26	46	4.86
C488441		0.91	0.31	2.97	45.1	90	1.67	0.23	0.55	4.63	24.4	16.6	37	3.25	53.3	3.97
C488442		0.45	0.29	3.05	41.6	120	1.56	0.17	0.32	8.07	36.8	12.9	38	2.89	45.1	4.42
C488443		0.15	0.35	3.32	141.5	100	1.61	0.19	0.37	13	31.7	13.9	40	3.1	51.1	5.61
C488444		1.24	0.05	0.16	<5	20	0.08	0.02	21.1	0.09	2.1	1.6	1	0.19	0.9	0.48
C488445		0.50	0.25	3.07	33.7	190	1.54	0.25	0.17	7.55	28	13.4	39	3.19	45.6	3.41
C488446		0.88	0.33	3.44	36.5	210	1.65	0.25	0.13	6.71	35.9	14.7	44	4.14	52.4	3.89
C488447		1.91	0.3	3.51	39.1	210	1.87	0.23	0.13	6.6	33.9	14.9	44	3.8	52.2	4.05
C488448		1.50	0.23	2.93	34.3	140	1.42	0.18	0.21	5.95	24.5	12.3	37	2.62	40.9	3.85
C488449		1.85	0.2	2.33	25.5	180	1.18	0.16	2.84	6.18	25.6	10.1	33	2	35.5	2.86
C488450		2.40	0.36	3.39	35.2	140	1.9	0.31	1.38	8.84	36.8	18.2	41	3.23	64.9	4.14

Comments: Interference: Ca>10% on ICP-MS As,ICP-AES results shown. REE's may not be totally soluble in MS61 method.

ALS Chemex

EXCELLENCE IN ANALYTICAL CHEMISTRY

ALS Canada Ltd.

212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO - RICH

Finalized Date: 9-OCT-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07099397

Sample Description	Method	ME-MS61	ME-MS61	ME-MS61	Hg-CV41	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61
	Analyte	Ga	Ge	Hf	Hg	In	K	La	Li	Mg	Mn	Mo	Na	Nb	Ni	P
	Units	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	%	ppm	ppm	%	ppm	ppm	ppm
	LOR	0.05	0.05	0.1	0.01	0.005	0.01	0.5	0.2	0.01	5	0.05	0.01	0.1	0.2	10
C488437		9.38	<0.05	1.5	0.27	0.05	1.01	13	5.9	0.27	94	39.1	0.03	5.8	108	300
C488438		8.99	<0.05	1.5	0.22	0.047	0.95	12.9	5	0.3	110	19.3	0.04	5.3	103	910
C488439		10.45	0.05	1.7	0.41	0.052	1.16	12.9	5	0.38	92	31.1	0.04	6.5	112.5	260
C488440		9.32	<0.05	1.7	0.33	0.042	1.02	11.2	5.1	0.34	89	34.4	0.03	6	99.9	380
C488441		9.19	0.06	1.6	0.32	0.048	0.98	11.7	5.4	0.4	118	44.6	0.02	6.1	110.5	270
C488442		8.26	0.05	1.5	0.28	0.048	0.91	18.3	5	0.27	160	35.6	0.03	5.9	117	300
C488443		8.98	0.1	1.6	0.37	0.119	0.98	14.2	5.3	0.25	148	79.2	0.03	6.3	227	750
C488444		0.93	0.1	<0.1	<0.01	<0.005	0.04	1	1.3	13.2	202	0.14	0.03	0.5	9	200
C488445		8.48	0.06	1.6	0.22	0.054	0.92	12.7	5.5	0.22	85	47	0.03	6.1	143.5	240
C488446		9.62	<0.05	1.7	0.26	0.067	1.09	16.3	5.2	0.21	106	51.2	0.04	6.6	155	240
C488447		10.25	0.07	1.8	0.28	0.065	1.14	15.1	6.1	0.22	106	45.9	0.04	7.3	142.5	260
C488448		7.58	<0.05	1.8	0.22	0.042	0.9	11.7	5.2	0.22	107	33.2	0.03	6.2	108	350
C488449		5.97	<0.05	1.3	0.18	0.04	0.67	12.6	4.3	0.42	120	27.9	0.03	4.5	98.4	300
C488450		9.64	0.05	1.6	0.32	0.073	0.99	16.9	6	0.26	101	31.1	0.03	6	110.5	390

Comments: Interference: Ca>10% on ICP-MS As,ICP-AES results shown. REE's may not be totally soluble in MS61 method.

ALS Chemex
EXCELLENCE IN ANALYTICAL CHEMISTRY
ALS Canada Ltd.
212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO - RICH

Finalized Date: 9-OCT-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07099397

Sample Description	Method	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61
	Analyte	Pb	Rb	Re	S	Sb	Sc	Se	Sn	Sr	Ta	Te	Th	Ti	Tl	U
	Units	ppm	ppm	ppm	%	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm
	LOR	0.5	0.1	0.002	0.01	0.05	0.1	1	0.2	0.2	0.05	0.05	0.2	0.005	0.02	0.1
C488437		13.1	55.2	0.035	4.06	1.7	8.3	7	1.2	40.4	0.37	0.18	3.7	0.168	3.76	12.2
C488438		10	50.3	0.025	4.24	1.67	8.2	5	1.1	48.9	0.35	0.13	3.4	0.161	2.55	6.6
C488439		14.8	61.3	0.041	6.38	3.01	8.7	6	1.4	39.1	0.41	0.29	3.8	0.191	5.54	6.6
C488440		11.9	55.6	0.046	5.24	2.16	9.2	7	1.2	41.5	0.38	0.26	3.5	0.172	4.03	8.4
C488441		12.4	55	0.055	4.24	1.81	8.2	8	1.2	49.9	0.39	0.27	2.8	0.161	4.51	10.5
C488442		11.6	49.5	0.043	4.29	1.63	7.2	8	1.1	43	0.36	0.17	3	0.163	3.67	9.7
C488443		13.2	53.2	0.11	5.67	2.52	10.8	12	1.4	44.9	0.4	0.25	3.6	0.166	4.46	12.1
C488444		1.4	1.4	<0.002	0.03	<0.05	0.8	3	<0.2	48.2	<0.05	<0.05	<0.2	0.012	<0.02	0.5
C488445		12.3	51.1	0.064	3.63	1.29	6.7	9	1.2	32.5	0.41	0.2	3.8	0.159	3.84	11.6
C488446		14.9	60.6	0.07	4.08	1.44	7.3	10	1.4	33.6	0.44	0.2	4	0.185	4.49	12.2
C488447		14	62.2	0.064	4.18	1.34	8.7	9	1.3	31.9	0.47	0.19	3.9	0.194	4.51	13
C488448		11.4	45.5	0.045	3.84	1.12	7.3	7	1.1	37.1	0.38	0.16	3.2	0.162	3.37	9.8
C488449		9	34.8	0.036	3.2	0.85	6.3	6	0.9	77.5	0.28	0.14	2.8	0.12	2.56	7.6
C488450		13.9	54.3	0.035	4.65	1.39	8.8	8	1.3	49.9	0.42	0.22	3.9	0.16	4.47	9.8

Comments: Interference: Ca>10% on ICP-MS As,ICP-AES results shown. REE's may not be totally soluble in MS61 method.

ALS Chemex

EXCELLENCE IN ANALYTICAL CHEMISTRY

ALS Canada Ltd.

212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO - RICH

Finalized Date: 9-OCT-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07099397

Sample Description	Method	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61
	Analyte	V	W	Y	Zn	Zr
	Units	ppm	ppm	ppm	ppm	ppm
	LOR	1	0.1	0.1	2	0.5
C488437		126	1.1	19	223	51.7
C488438		120	0.8	28.4	535	48.2
C488439		134	0.8	15.2	147	58.8
C488440		118	0.8	16.4	109	55.5
C488441		124	0.9	22	177	55.5
C488442		176	0.7	22.9	261	51.9
C488443		193	0.8	31.2	1795	54.8
C488444		6	0.1	1.2	16	<0.5
C488445		148	0.9	23.8	161	54.4
C488446		162	1	27.5	242	60.7
C488447		166	1	28.2	207	63.9
C488448		130	0.7	17.6	147	54.7
C488449		104	0.6	19.7	230	43
C488450		125	1	25.8	338	55.6

Comments: Interference: Ca>10% on ICP-MS As,ICP-AES results shown. REE's may not be totally soluble in MS61 method.

ALS Chemex
EXCELLENCE IN ANALYTICAL CHEMISTRY
ALS Canada Ltd.
212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Finalized Date: 17-SEP-2007
Account: MTT

CERTIFICATE VA07099396

Project: NIMO - RICH

P.O. No.: R107-16

This report is for 11 Drill Core samples submitted to our lab in Vancouver, BC, Canada on 13-AUG-2007.

The following have access to data associated with this certificate:

AL ARCHER VANCOUVER OFFICE	DOUG EATON BILL WENGZYNOWSKI	JOAN MARIACHER

SAMPLE PREPARATION

ALS CODE	DESCRIPTION
WEI-21	Received Sample Weight
LOG-22	Sample login - Rcd w/o BarCode
PUL-QC	Pulverizing QC Test
CRU-31	Fine crushing - 70% <2mm
SPL-21	Split sample - riffle splitter
PUL-31	Pulverize split to 85% <75 um

ANALYTICAL PROCEDURES

ALS CODE	DESCRIPTION	
ME-MS61	48 element four acid ICP-MS	
Hg-CV41	Trace Hg - cold vapor/AAS	FIMS

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

This is the Final Report and supersedes any preliminary report with this certificate number. Results apply to samples as submitted. All pages of this report have been checked and approved for release.

Signature:

Lawrence Ng, Laboratory Manager - Vancouver

ALS Chemex

EXCELLENCE IN ANALYTICAL CHEMISTRY

ALS Canada Ltd.

212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: STRATEGIC METALS LTD.
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO - RICH

Finalized Date: 17-SEP-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07099396

Sample Description	Method / Analyte / Units / LOR	WEI-21 Recvd Wt. kg 0.02	ME-MS61 Ag ppm 0.01	ME-MS61 Al % 0.01	ME-MS61 As ppm 0.2	ME-MS61 Ba ppm 10	ME-MS61 Be ppm 0.05	ME-MS61 Bi ppm 0.01	ME-MS61 Ca % 0.01	ME-MS61 Cd ppm 0.02	ME-MS61 Ce ppm 0.01	ME-MS61 Co ppm 0.1	ME-MS61 Cr ppm 1	ME-MS61 Cs ppm 0.05	ME-MS61 Cu ppm 0.2	ME-MS61 Fe % 0.01
C488403		2.30	0.14	1.44	11.8	340	0.96	0.09	0.04	1.22	12.35	3.8	37	1.78	27.6	1.17
C488404		1.56	0.15	1.61	14.9	470	1.09	0.08	0.07	0.90	14.60	4.5	33	1.77	33.0	1.31
C488405		0.94	0.22	1.77	23.0	220	1.18	0.09	0.05	1.17	17.40	6.7	32	2.00	50.5	1.87
C488406		1.38	0.21	1.58	15.2	310	1.07	0.10	0.13	3.21	13.90	4.8	36	1.92	29.7	1.48
C488407		0.82	0.31	1.98	47.4	300	1.20	0.11	0.05	5.11	17.95	8.9	41	2.33	53.9	2.08
C488409		1.10	0.61	7.00	71.2	140	3.51	0.26	0.55	6.63	48.90	15.4	82	11.00	75.1	3.78
C488410		0.53	0.02	0.12	5	40	0.09	0.17	21.90	0.14	1.84	2.1	2	0.21	2.6	0.52
C488411		1.10	0.31	3.40	30.1	370	1.40	0.13	5.49	4.59	35.70	7.3	52	4.41	35.1	1.86
C488412		1.88	0.05	0.93	<5	830	0.52	0.06	25.40	0.49	11.70	2.2	8	0.93	7.4	0.49
C488413		2.68	0.34	4.59	26.7	300	1.64	0.16	3.87	4.80	37.50	8.9	54	5.94	35.5	2.46
C488414		2.85	0.30	4.56	19.6	270	1.90	0.15	2.15	3.76	33.20	8.6	51	5.79	30.2	2.15

Comments: Interference: Ca>10% on ICP-MS As,ICP-AES results shown. REE's may not be totally soluble in MS61 method.

ALS Chemex

EXCELLENCE IN ANALYTICAL CHEMISTRY

ALS Canada Ltd.

212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO - RICH

Finalized Date: 17-SEP-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07099396

Sample Description	Method / Analyte / Units / LOR	ME-MS61 Ga ppm 0.05	ME-MS61 Ge ppm 0.05	ME-MS61 Hf ppm 0.1	Hg-CV41 Hg ppm 0.01	ME-MS61 In ppm 0.005	ME-MS61 K % 0.01	ME-MS61 La ppm 0.5	ME-MS61 Li ppm 0.2	ME-MS61 Mg % 0.01	ME-MS61 Mn ppm 5	ME-MS61 Mo ppm 0.05	ME-MS61 Na % 0.01	ME-MS61 Nb ppm 0.1	ME-MS61 Ni ppm 0.2	ME-MS61 P ppm 10
C488403		3.38	<0.05	0.7	0.04	0.009	0.47	8.3	7.4	0.09	49	50.30	0.04	2.9	146.0	190
C488404		3.67	<0.05	0.8	0.06	0.011	0.54	10.2	11.5	0.10	49	54.70	0.04	3.1	158.5	350
C488405		4.30	0.07	0.9	0.11	0.013	0.59	11.1	11.0	0.11	64	74.70	0.03	3.4	193.0	250
C488406		4.07	0.06	0.9	0.06	0.018	0.50	8.1	11.7	0.15	71	43.20	0.04	3.1	149.5	200
C488407		5.83	0.15	1.2	0.13	0.028	0.65	10.4	16.6	0.13	73	54.90	0.04	4.0	735.0	240
C488409		25.20	0.26	3.0	0.18	0.112	2.49	27.1	16.1	0.55	135	79.50	0.06	11.2	263.0	430
C488410		0.36	0.07	<0.1	<0.01	<0.005	0.04	0.9	1.4	13.45	191	1.53	0.01	0.3	10.8	220
C488411		9.48	0.13	1.5	0.10	0.040	1.19	22.6	10.4	0.33	131	33.80	0.04	5.5	135.0	400
C488412		2.24	0.06	0.4	0.02	0.008	0.26	7.9	2.0	6.52	418	7.07	0.10	1.6	22.4	1810
C488413		12.50	0.11	2.0	0.10	0.040	1.57	21.5	8.8	0.67	174	31.20	0.07	7.2	109.0	230
C488414		12.45	0.17	1.9	0.10	0.037	1.66	18.9	8.2	0.50	113	27.10	0.05	7.0	98.4	230

Comments: Interference: Ca>10% on ICP-MS As,ICP-AES results shown. REE's may not be totally soluble in MS61 method.

ALS Chemex

EXCELLENCE IN ANALYTICAL CHEMISTRY

ALS Canada Ltd.

212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO - RICH

Finalized Date: 17-SEP-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07099396

Sample Description	Method	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61
	Analyte	Pb	Rb	Re	S	Sb	Sc	Se	Sn	Sr	Ta	Te	Th	Ti	Tl	U
	Units	ppm	ppm	ppm	%	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm
	LOR	0.5	0.1	0.002	0.01	0.05	0.1	1	0.2	0.2	0.05	0.05	0.2	0.005	0.02	0.1
C488403		4.5	25.1	0.040	0.89	3.21	3.4	9	0.6	36.7	0.15	0.10	1.7	0.066	2.13	8.6
C488404		5.3	27.4	0.042	1.08	3.68	3.8	12	0.6	54.2	0.17	0.11	1.9	0.075	2.81	9.2
C488405		7.6	31.2	0.061	1.56	6.58	4.6	15	0.7	45.6	0.18	0.13	2.0	0.085	5.22	11.6
C488406		4.8	27.9	0.047	1.18	5.42	4.1	13	0.7	60.9	0.17	0.10	1.9	0.077	2.75	7.9
C488407		7.7	34.8	0.369	1.86	8.71	5.4	36	0.9	88.1	0.23	0.40	2.4	0.102	6.12	8.2
C488409		17.3	158.0	0.095	3.93	16.20	14.8	59	2.6	60.3	0.68	0.25	7.9	0.322	10.40	14.4
C488410		1.9	1.9	0.006	0.09	0.17	0.6	3	<0.2	52.6	<0.05	<0.05	<0.2	0.005	0.11	0.6
C488411		7.7	67.3	0.041	2.01	7.39	7.1	23	1.3	178.5	0.33	0.11	3.9	0.166	3.85	6.9
C488412		2.0	15.2	0.005	0.52	2.22	2.5	5	0.3	1060.0	0.08	<0.05	1.2	0.042	0.70	2.3
C488413		10.4	92.2	0.028	2.50	8.03	9.4	17	1.6	133.5	0.45	0.08	5.4	0.218	4.32	5.3
C488414		10.2	91.5	0.021	2.18	6.09	8.6	11	1.5	97.5	0.48	0.09	5.6	0.228	4.08	5.0

Comments: Interference: Ca>10% on ICP-MS As,ICP-AES results shown. REE's may not be totally soluble in MS61 method.

ALS Chemex
EXCELLENCE IN ANALYTICAL CHEMISTRY
ALS Canada Ltd.
212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: STRATEGIC METALS LTD.
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO - RICH

Finalized Date: 17-SEP-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07099396

Sample Description	Method	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61
	Analyte	V	W	Y	Zn	Zr
	Units	ppm	ppm	ppm	ppm	ppm
	LOR	1	0.1	0.1	2	0.5
C488403		271	0.7	11.2	152	25.6
C488404		175	0.8	10.4	129	28.7
C488405		255	0.6	16.6	159	33.5
C488406		563	0.5	14.7	369	30.9
C488407		523	0.5	14.6	594	41.1
C488409		1425	1.2	24.4	654	93.3
C488410		11	0.1	1.3	25	0.9
C488411		606	0.6	27.9	435	50.3
C488412		97	0.2	16.4	38	14.7
C488413		644	0.8	18.6	359	61.0
C488414		623	0.8	14.1	314	63.4

Comments: Interference: Ca>10% on ICP-MS As,ICP-AES results shown. REE's may not be totally soluble in MS61 method.

ALS Chemex
EXCELLENCE IN ANALYTICAL CHEMISTRY
ALS Canada Ltd.
212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Finalized Date: 4-OCT-2007
Account: MTT

CERTIFICATE VA07099395

Project: NIMO-RICH

P.O. No.: R107-14B

This report is for 13 Drill Core samples submitted to our lab in Vancouver, BC, Canada on 31-AUG-2007.

The following have access to data associated with this certificate:

AL ARCHER VANCOUVER OFFICE	DOUG EATON BILL WENGZYNOWSKI	JOAN MARIACHER

SAMPLE PREPARATION

ALS CODE	DESCRIPTION
WEI-21	Received Sample Weight
LOG-22	Sample login - Rcd w/o BarCode
CRU-31	Fine crushing - 70% <2mm
SPL-21	Split sample - riffle splitter
PUL-32	Pulverize 1000g to 85% < 75 um
BAG-01	Bulk Master for Storage

ANALYTICAL PROCEDURES

ALS CODE	DESCRIPTION	
ME-MS61	48 element four acid ICP-MS	
Hg-CV41	Trace Hg - cold vapor/AAS	FIMS

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

This is the Final Report and supersedes any preliminary report with this certificate number. Results apply to samples as submitted. All pages of this report have been checked and approved for release.

Signature:

Lawrence Ng, Laboratory Manager - Vancouver

ALS Chemex
EXCELLENCE IN ANALYTICAL CHEMISTRY
ALS Canada Ltd.
212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: STRATEGIC METALS LTD.
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO-RICH

Finalized Date: 4-OCT-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07099395

Sample Description	Method	WEI-21	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61
	Analyte	Recvd Wt.	Ag	Al	As	Ba	Be	Bi	Ca	Cd	Ce	Co	Cr	Cs	Cu	Fe
	Units	kg	ppm	%	ppm	ppm	ppm	ppm	%	ppm	ppm	ppm	ppm	ppm	ppm	%
	LOR	0.02	0.01	0.01	0.2	10	0.05	0.01	0.01	0.02	0.01	0.1	1	0.05	0.2	0.01
C488337		0.70	0.29	1.28	10.9	610	0.83	0.06	0.06	7.91	9.4	2.9	49	1.5	33.5	1.09
C488338		0.40	0.17	1.36	8.7	560	0.88	0.05	0.05	2.89	9.78	2.8	34	1.57	20.6	1
C488339		0.42	0.12	1.41	12.6	470	1.02	0.07	0.04	1.86	10.5	4.3	45	1.53	26	2.09
C488340		0.70	0.19	1.53	16.3	360	0.92	0.07	0.04	2.91	9.87	4.3	40	1.72	27.4	1.58
C488341		1.04	0.49	5.87	64.1	100	3.25	0.22	0.13	7.38	43.8	12.6	94	9.05	60.6	3.42
C488342		1.01	0.37	5.45	41.9	210	2.39	0.17	2.39	4.06	46.4	9.9	60	7.04	49.6	2.85
C488343		1.06	0.06	0.94	13	1770	0.76	0.02	33	0.42	12.4	2	12	0.98	6.2	0.42
C488344		1.72	0.21	3.73	23.1	330	1.5	0.11	8.28	3.54	33.9	6.8	55	4.91	26.9	2.06
C488345		1.52	0.27	4.53	18.9	390	1.51	0.14	4.47	4.05	39.6	7.9	60	5.83	28.3	2.11
C488346		1.65	0.28	5.25	21.1	160	2.04	0.17	3.95	3.4	43.3	9.2	59	6.96	32.2	2.55
C488348		1.11	0.01	0.08	5	20	0.09	0.02	21.1	0.07	1.37	1.6	4	0.18	2.1	0.49
C488349		1.89	0.31	5.35	22.4	190	2.11	0.18	1.1	3.07	38.9	9.8	63	7.06	34.1	2.64
C488350		2.63	0.3	4.22	22.1	250	1.54	0.13	2.29	3.35	33.9	8	58	4.99	32.6	2.4

Comments: Interference: Ca>10% on ICP-MS As,ICP-AES results shown. REE's may not be totally soluble in MS61 method.

ALS Chemex

EXCELLENCE IN ANALYTICAL CHEMISTRY

ALS Canada Ltd.

212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO-RICH

Finalized Date: 4-OCT-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07099395

Sample Description	Method	ME-MS61	ME-MS61	ME-MS61	Hg-CV41	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61
	Analyte	Ga	Ge	Hf	Hg	In	K	La	Li	Mg	Mn	Mo	Na	Nb	Ni	P
	Units	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	%	ppm	ppm	%	ppm	ppm	ppm
	LOR	0.05	0.05	0.1	0.01	0.005	0.01	0.5	0.2	0.01	5	0.05	0.01	0.1	0.2	10
C488337		3.07	0.07	0.6	0.06	0.012	0.35	6.8	5.8	0.09	47	34.5	0.04	2.3	113	200
C488338		2.76	0.06	0.6	0.04	0.009	0.4	6.4	5.6	0.1	43	28.4	0.04	2.1	106	140
C488339		2.98	0.09	0.7	0.06	0.009	0.37	6.4	8.1	0.08	102	41.4	0.04	2.8	158.5	220
C488340		3.9	0.11	0.8	0.08	0.011	0.4	5.5	12.1	0.1	72	36.1	0.03	2.9	163.5	220
C488341		17.45	0.3	2.4	0.21	0.104	1.8	25.5	11.9	0.46	119	73.6	0.1	9.7	451	250
C488342		14.25	0.23	2.2	0.19	0.052	1.66	29.5	9.4	0.45	131	46	0.09	8.8	152	350
C488343		2.27	0.09	0.4	0.03	0.007	0.26	8.4	2.2	0.45	248	6.82	0.12	1.8	13.9	1080
C488344		8.99	0.14	1.6	0.11	0.038	1.14	20.9	7.4	0.94	226	27.4	0.12	6.2	87.6	380
C488345		11.05	0.15	1.8	0.10	0.044	1.37	24.2	6.9	0.37	103	28.2	0.11	7.1	90.7	200
C488346		13.6	0.17	2.2	0.11	0.048	1.62	25	7.3	0.58	129	29	0.13	8.8	94.4	290
C488348		0.34	0.17	<0.1	<0.01	<0.005	0.03	0.7	1	13.05	219	0.28	0.01	0.3	<0.2	180
C488349		13.6	0.15	2.1	0.11	0.043	1.63	22.7	7.7	0.46	95	34.6	0.11	8.4	120	250
C488350		9.9	0.15	1.8	0.12	0.036	1.24	21.4	5.7	0.5	103	37.6	0.1	6.4	134	250

Comments: Interference: Ca>10% on ICP-MS As,ICP-AES results shown. REE's may not be totally soluble in MS61 method.

ALS Chemex

EXCELLENCE IN ANALYTICAL CHEMISTRY

ALS Canada Ltd.

212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO-RICH

Finalized Date: 4-OCT-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07099395

Sample Description	Method	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61
	Analyte	Pb	Rb	Re	S	Sb	Sc	Se	Sn	Sr	Ta	Te	Th	Ti	Tl	U
	Units	ppm	ppm	ppm	%	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm
	LOR	0.5	0.1	0.002	0.01	0.05	0.1	1	0.2	0.2	0.05	0.05	0.2	0.005	0.02	0.1
C488337		4.3	23	0.04	0.68	9.05	2.6	10	0.5	42.2	0.16	0.09	1.7	0.054	2.27	5.6
C488338		3.7	24.1	0.03	0.68	4.33	2.6	7	0.4	42.8	0.13	0.05	1.7	0.057	1.61	5.9
C488339		4.6	23	0.039	0.87	3.15	3.3	10	0.8	69.8	0.16	0.08	1.8	0.058	2.12	8.8
C488340		4.7	26.3	0.041	0.97	3.83	3.6	19	0.7	103.5	0.18	0.11	2.1	0.07	2.68	7.9
C488341		14.5	126.5	0.141	3.35	14.25	11.6	58	2.5	54.9	0.67	0.16	7.4	0.27	8.71	14
C488342		14.3	107.5	0.049	2.93	11.6	10.6	35	1.8	91.4	0.62	0.1	7.1	0.25	5.92	8.8
C488343		2.1	17	0.007	0.53	1.27	3.7	6	0.3	388	0.1	<0.05	1.2	0.044	0.67	1.7
C488344		8	71.5	0.029	1.99	5.83	7.4	17	1.4	358	0.41	0.07	5	0.173	3.38	5
C488345		9.7	87.5	0.028	2.21	6.27	8.5	12	1.5	122	0.49	0.07	6	0.206	3.75	5.1
C488346		11.6	103.5	0.021	2.67	6.66	10.2	13	1.8	121.5	0.62	0.07	6.9	0.247	3.96	5.2
C488348		1.7	1.5	<0.002	0.04	0.07	0.5	1	<0.2	51.4	<0.05	<0.05	<0.2	<0.005	<0.02	0.6
C488349		11.4	104.5	0.029	2.64	5.87	10.6	12	1.8	67.3	0.59	0.07	6.7	0.244	4.5	5.7
C488350		9.9	76.7	0.038	2.51	5.41	8.2	11	1.4	100	0.45	0.09	5.4	0.202	4.6	6.4

Comments: Interference: Ca>10% on ICP-MS As,ICP-AES results shown. REE's may not be totally soluble in MS61 method.

ALS Chemex
EXCELLENCE IN ANALYTICAL CHEMISTRY
ALS Canada Ltd.
212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: STRATEGIC METALS LTD.
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO-RICH

Finalized Date: 4-OCT-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07099395

Sample Description	Method	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61
	Analyte	V	W	Y	Zn	Zr
	Units	ppm	ppm	ppm	ppm	ppm
	LOR	1	0.1	0.1	2	0.5
C488337		546	0.4	9.1	481	24.3
C488338		324	0.4	12.1	155	20.5
C488339		271	0.6	13.4	189	28.7
C488340		510	0.4	10	418	29.4
C488341		1195	1.1	21.8	965	76.5
C488342		861	1	33.4	394	71.2
C488343		106	0.2	21	32	17.5
C488344		525	0.7	21.7	289	55.4
C488345		589	0.8	28.9	337	58
C488346		620	1	31.4	278	67.4
C488348		5	0.1	1	15	0.5
C488349		671	0.9	14.7	255	65.4
C488350		678	0.8	14.7	287	57.2

Comments: Interference: Ca>10% on ICP-MS As,ICP-AES results shown. REE's may not be totally soluble in MS61 method.

ALS Chemex
EXCELLENCE IN ANALYTICAL CHEMISTRY
ALS Canada Ltd.
212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Finalized Date: 9-OCT-2007
Account: MTT

CERTIFICATE VA07099394

Project: NIMO - RICH

P.O. No.: R107-14A

This report is for 20 Drill Core samples submitted to our lab in Vancouver, BC, Canada on 31-AUG-2007.

The following have access to data associated with this certificate:

AL ARCHER VANCOUVER OFFICE	DOUG EATON BILL WENGZYNOWSKI	JOAN MARIACHER

SAMPLE PREPARATION

ALS CODE	DESCRIPTION
WEI-21	Received Sample Weight
LOG-22	Sample login - Rcd w/o BarCode
CRU-31	Fine crushing - 70% <2mm
SPL-21	Split sample - riffle splitter
PUL-31	Pulverize split to 85% <75 um

ANALYTICAL PROCEDURES

ALS CODE	DESCRIPTION	
ME-MS61	48 element four acid ICP-MS	
Hg-CV41	Trace Hg - cold vapor/AAS	FIMS

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

s is the Final Report and supersedes any preliminary report with this certificate number. Results apply to samples as submitted. All ges of this report have been checked and approved for release.

Signature:



Lawrence Ng, Laboratory Manager - Vancouver

ALS Chemex

EXCELLENCE IN ANALYTICAL CHEMISTRY

ALS Canada Ltd.

212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO - RICH

Finalized Date: 9-OCT-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07099394

Sample Description	Method	WEI-21	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61
	Analyte	Recvd Wt.	Ag	Al	As	Ba	Be	Bi	Ca	Cd	Ce	Co	Cr	Cs	Cu	Fe
	Units	kg	ppm	%	ppm	ppm	ppm	ppm	%	ppm	ppm	ppm	ppm	ppm	ppm	%
	LOR	0.02	0.01	0.01	0.2	10	0.05	0.01	0.01	0.02	0.01	0.1	1	0.05	0.2	0.01
C488371		0.84	0.66	1.72	18.6	500	1.06	0.11	0.09	22.1	13.85	3	44	1.65	45.9	0.91
C488372		1.17	0.87	1.58	25.3	580	0.96	0.08	0.08	10.85	15.15	3.9	40	1.6	46.2	1.13
C488373		0.58	0.49	1.51	12.5	1230	0.95	0.32	0.09	10.15	11.95	2.7	38	1.68	31.1	0.74
C488374		0.72	0.53	1.73	14.2	320	1.01	0.07	0.05	12.55	11.65	3.6	43	1.86	45.8	0.86
C488375		0.51	0.48	1.64	18.7	320	1.18	0.23	0.1	11.95	12.95	3.9	53	1.45	56.3	0.89
C488376		0.69	0.52	2.19	30	210	1.42	0.1	0.12	7.31	15.75	5.7	52	1.87	52.6	1.49
C488377		0.45	0.19	1.64	12.5	340	1.13	0.09	0.05	2.65	8.6	3.6	38	1.38	25	0.96
C488378		0.50	0.21	1.75	17.7	420	1.13	0.09	0.68	19.45	11.55	4.6	43	1.62	29.4	1.09
C488379		0.44	0.22	1.67	19.4	230	0.9	0.08	0.08	10.85	9.6	4.3	41	1.47	29.8	1.08
C488380		0.62	0.43	6.89	83.9	180	3.15	0.29	0.16	6.64	8	15.3	89	9.7	54.1	3.59
C488381		0.57	0.52	5.87	52.3	110	2.71	0.29	0.16	7.17	40.5	13.2	92	8.2	60	3.2
C488382		0.55	0.48	6.04	46.9	380	2.37	0.27	0.85	4.59	48.5	13.6	73	8.24	54.5	3.22
C488383		0.95	0.2	2.65	20	920	1.07	0.09	16.15	1.67	34.8	5.3	34	2.7	19.2	1.26
C488384		1.47	0.03	0.07	<5	30	0.08	0.15	21.3	0.07	1.15	1.5	1	0.16	1.2	0.43
C488385		0.93	0.33	5.85	33.5	390	2.06	0.19	9.26	4.32	49.7	10.8	73	7.14	36.3	2.52
C488386		1.77	0.3	4.07	23	370	1.48	0.16	3.41	4.35	31.7	8	56	4.8	30.5	2.07
C488387		1.65	0.29	4.87	20.4	350	1.74	0.15	6.52	3.19	41.8	9.6	60	5.33	29.9	2.28
C488388		1.01	0.21	3.96	15	620	1.32	0.15	15.75	2.1	29.4	8.1	41	4.26	21.9	1.65
C488389		2.47	0.3	4.61	22.3	280	1.7	0.15	2.4	3.16	36.4	10.2	60	5.3	33.8	2.24
C488390		2.14	0.27	3.78	22.3	360	1.41	0.15	4.39	3.52	37.2	9.9	60	3.99	35.1	2.18

Comments: Interference: Ca>10% on ICP-MS As,ICP-AES results shown. REE's may not be totally soluble in MS61 method.

ALS Chemex
EXCELLENCE IN ANALYTICAL CHEMISTRY
ALS Canada Ltd.
212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO - RICH

Finalized Date: 9-OCT-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07099394

Sample Description	Method	ME-MS61	ME-MS61	ME-MS61	Hg-CV41	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61
	Analyte	Ga	Ge	Hf	Hg	In	K	La	Li	Mg	Mn	Mo	Na	Nb	Ni	P
	Units	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	%	ppm	ppm	%	ppm	ppm	ppm
	LOR	0.05	0.05	0.1	0.01	0.005	0.01	0.5	0.2	0.01	5	0.05	0.01	0.1	0.2	10
C488371		4.51	0.12	0.6	0.14	0.017	0.45	8.4	18.7	0.1	32	29.9	0.03	3	144.5	520
C488372		3.89	0.15	0.6	0.10	0.013	0.41	11	13.3	0.08	41	38.4	0.03	2.6	276	420
C488373		3.94	0.11	0.5	0.09	0.018	0.41	8	11.5	0.1	34	26.5	0.02	2.2	161.5	260
C488374		4.76	0.05	0.6	0.10	0.02	0.48	7.8	7.9	0.1	32	35.1	0.03	2.7	152	240
C488375		3.94	0.07	0.7	0.09	0.02	0.4	7.4	54.2	0.09	28	46	0.02	2.6	226	830
C488376		5.13	0.06	0.9	0.10	0.017	0.59	11	40.6	0.14	47	45.1	0.02	3.5	315	580
C488377		2.77	<0.05	0.6	0.04	0.011	0.33	5.4	11.2	0.07	38	34	0.03	2.2	248	240
C488378		3.51	0.05	0.7	0.09	0.013	0.39	6.1	61.1	0.09	48	36.7	0.03	2.9	195.5	640
C488379		4.23	0.07	0.7	0.08	0.017	0.39	4.9	71.2	0.09	44	39.1	0.02	2.7	216	710
C488380		21	0.3	2.3	0.16	0.101	2.02	1.7	15	0.49	111	68.6	0.12	10.3	689	620
C488381		17.5	0.18	2	0.20	0.092	1.75	23.2	10.4	0.46	137	63.7	0.03	8.7	262	250
C488382		16.7	0.14	2.2	0.19	0.074	1.72	29.6	9.7	0.54	180	52.7	0.05	9.3	221	390
C488383		6.66	0.11	1	0.07	0.021	0.8	22	4.1	0.7	246	21.6	0.07	4.3	81.5	330
C488384		0.64	0.15	<0.1	<0.01	0.015	0.03	0.6	1	13.3	191	0.17	<0.01	0.2	8.8	190
C488385		14.75	0.12	2.2	0.14	0.056	1.75	30.4	7.6	0.53	165	33	0.07	9.2	130	450
C488386		10.55	0.05	1.5	0.11	0.042	1.22	19.2	5.9	0.79	175	30	0.07	6	116.5	190
C488387		12.35	0.07	1.8	0.11	0.038	1.39	23.9	6.6	0.75	183	28.3	0.11	7.4	110.5	240
C488388		9.96	<0.05	1.5	0.08	0.03	1.19	17.4	5.8	0.37	232	19.7	0.07	5.8	82.8	270
C488389		12.1	0.06	1.7	0.11	0.04	1.37	21.3	7.1	0.48	105	35.9	0.06	6.9	147.5	210
C488390		9.43	0.05	1.7	0.10	0.032	1.15	22.8	7.2	0.82	175	41.4	0.08	6.2	180	350

Comments: Interference: Ca>10% on ICP-MS As,ICP-AES results shown. REE's may not be totally soluble in MS61 method.

ALS Chemex
EXCELLENCE IN ANALYTICAL CHEMISTRY
ALS Canada Ltd.
212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO - RICH

Finalized Date: 9-OCT-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07099394

Sample Description	Method	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61
	Analyte	Pb	Rb	Re	S	Sb	Sc	Se	Sn	Sr	Ta	Te	Th	Ti	Tl	U
	Units	ppm	ppm	ppm	%	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm
	LOR	0.5	0.1	0.002	0.01	0.05	0.1	1	0.2	0.2	0.05	0.05	0.2	0.005	0.02	0.1
C488371		5.2	28.5	0.027	0.98	16.75	3.4	20	0.6	99.9	0.18	0.09	2	0.071	1.9	6.3
C488372		5.4	27	0.081	1.15	14.75	3.3	21	0.5	74.4	0.15	0.16	1.8	0.063	2.88	6.1
C488373		5.2	27.6	0.033	0.75	12.35	3	15	0.5	85.9	0.14	0.08	1.7	0.06	1.64	4.8
C488374		5	30.9	0.047	0.85	16.3	3.8	13	0.7	63.1	0.17	0.12	1.9	0.072	2.14	5.5
C488375		5.8	23.1	0.05	0.94	14.4	5	14	0.7	293	0.15	0.15	2.2	0.065	3.62	11
C488376		6	34.7	0.068	1.51	14.95	5.6	19	0.7	147	0.22	0.24	2.3	0.092	4.3	9.2
C488377		3.6	20.8	0.034	0.79	4.78	3.1	8	0.5	63.4	0.13	0.08	1.4	0.05	1.63	8.5
C488378		4.5	22.5	0.037	1.1	4.44	4.8	13	1.3	382	0.18	0.1	2.2	0.072	2.46	9.6
C488379		4.7	22.3	0.06	1.08	4.52	4.5	22	0.7	452	0.17	0.21	1.8	0.072	3.4	9.3
C488380		12.5	141.5	0.193	3.83	15.35	13.6	72	2.6	195	0.66	0.24	2.5	0.3	10.15	13.3
C488381		15.4	122	0.072	3.17	12.95	11.2	42	2.3	40.6	0.58	0.12	6.4	0.26	7.99	10.7
C488382		15.9	124	0.05	3.19	13.5	10.6	34	2.2	74.3	0.6	0.11	6.7	0.267	6.51	8.5
C488383		5.9	49.3	0.023	1.48	3.91	5.3	15	0.9	484	0.28	0.07	3.4	0.124	2.32	4.9
C488384		1.6	1.3	<0.002	0.02	0.06	0.6	3	<0.2	49.5	<0.05	<0.05	<0.2	<0.005	<0.02	0.6
C488385		12.3	111.5	0.03	2.86	8.63	10	24	1.9	233	0.6	0.1	7.1	0.271	4.95	6.2
C488386		9.8	78.5	0.032	2.21	6.76	7.6	14	1.5	140.5	0.4	0.08	4.8	0.183	4.04	5.2
C488387		10.7	89.3	0.023	2.57	6.08	9.6	12	1.6	201	0.49	0.08	5.6	0.217	3.72	5.1
C488388		7.9	71.2	0.016	1.95	4.35	7.8	8	1.3	540	0.39	0.07	4.6	0.17	2.8	3.5
C488389		10.1	87.9	0.033	2.41	4.99	9.5	11	1.7	91.3	0.44	0.09	5.3	0.21	4.62	5.9
C488390		9.2	68	0.042	2.45	4.6	8	11	1.4	158	0.41	0.11	4.8	0.189	4.31	8.2

Comments: Interference: Ca>10% on ICP-MS As,ICP-AES results shown. REE's may not be totally soluble in MS61 method.

ALS Chemex
EXCELLENCE IN ANALYTICAL CHEMISTRY
ALS Canada Ltd.
212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO - RICH

Finalized Date: 9-OCT-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07099394

Sample Description	Method	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61
	Analyte	V	W	Y	Zn	Zr
	Units	ppm	ppm	ppm	ppm	ppm
	LOR	1	0.1	0.1	2	0.5
C488371		823	0.4	13.1	993	22.6
C488372		558	9.8	11.4	521	22.5
C488373		678	1.1	8.2	689	17.2
C488374		905	0.6	9.1	950	25.5
C488375		866	0.4	14.7	825	28.1
C488376		660	0.5	14.7	475	36.5
C488377		310	0.5	14.4	362	22.4
C488378		667	0.9	13.4	403	27.9
C488379		639	0.4	11.8	501	27.6
C488380		981	1.2	23.2	891	81.7
C488381		1300	1	22.3	1080	68.8
C488382		1045	1	21.4	609	72.8
C488383		346	0.5	69.9	164	37.7
C488384		4	0.1	0.9	16	0.5
C488385		774	1	44.2	347	73
C488386		608	0.8	13.2	364	51.1
C488387		585	0.8	27.2	299	59.5
C488388		420	0.6	23.8	199	47.4
C488389		667	0.8	18	367	58.1
C488390		761	0.8	27.3	481	58.4

Comments: Interference: Ca>10% on ICP-MS As,ICP-AES results shown. REE's may not be totally soluble in MS61 method.

ALS Chemex
EXCELLENCE IN ANALYTICAL CHEMISTRY
ALS Canada Ltd.
212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Finalized Date: 2-OCT-2007
Account: MTT

CERTIFICATE VA07099393

Project: NIMO - RICH

P.O. No.: R107-19

This report is for 12 Drill Core samples submitted to our lab in Vancouver, BC, Canada on 31-AUG-2007.

The following have access to data associated with this certificate:

AL ARCHER VANCOUVER OFFICE	DOUG EATON BILL WENGZYNOWSKI	JOAN MARIACHER

SAMPLE PREPARATION

ALS CODE	DESCRIPTION
WEI-21	Received Sample Weight
LOG-22	Sample login - Rcd w/o BarCode
CRU-31	Fine crushing - 70% <2mm
SPL-21	Split sample - riffle splitter
PUL-31	Pulverize split to 85% <75 um

ANALYTICAL PROCEDURES

ALS CODE	DESCRIPTION	
ME-MS61	48 element four acid ICP-MS	
Hg-CV41	Trace Hg - cold vapor/AAS	FIMS

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

This is the Final Report and supersedes any preliminary report with this certificate number. Results apply to samples as submitted. All pages of this report have been checked and approved for release.

Signature:

Lawrence Ng, Laboratory Manager - Vancouver

ALS Chemex

EXCELLENCE IN ANALYTICAL CHEMISTRY

ALS Canada Ltd.

212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO - RICH

Finalized Date: 2-OCT-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07099393

Sample Description	Method	WEI-21	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61
	Analyte	Recvd Wt.	Ag	Al	As	Ba	Be	Bi	Ca	Cd	Ce	Co	Cr	Cs	Cu	Fe
	Units	kg	ppm	%	ppm	ppm	ppm	ppm	%	ppm	ppm	ppm	ppm	ppm	ppm	%
	LOR	0.02	0.01	0.01	0.2	10	0.05	0.01	0.01	0.02	0.01	0.1	1	0.05	0.2	0.01
C488391		2.63	0.19	1.52	17.1	430	1.13	0.05	0.09	1.1	13.2	5.7	41	1.7	25.8	0.98
C488392		2.10	0.12	1.4	13.2	490	0.88	0.04	0.07	0.72	12	5.1	39	1.42	22.1	0.95
C488393		1.88	0.1	1.62	14.2	350	0.81	0.03	0.07	0.73	11.9	4.2	42	1.18	27.4	1.14
C488394		1.78	0.23	1.77	20.7	340	1.15	0.06	0.15	2.65	15.3	6	43	1.89	31.9	1.38
C488395		0.81	0.36	2.2	32.9	370	1.34	0.09	0.06	4.44	17.8	7.6	54	2.19	49.4	1.78
C488396		0.27	0.5	3.1	375	320	1.4	0.25	1.08	18.15	24.1	32.4	53	3.55	80.1	3.57
C488397		0.82	0.07	0.8	12	510	1.06	0.02	33.5	0.94	13.1	2.5	9	0.83	8.5	0.36
C488398		0.93	0.11	2.01	8	720	0.76	0.05	15.8	1.23	15.85	4.5	19	2.22	15.2	1.11
C488399		1.77	0.29	4.54	31.6	560	1.85	0.17	2.88	4.38	40.4	8.5	59	5.34	34.4	1.91
C488400		1.96	0.28	4.92	31.5	600	2.1	0.23	2.9	4.65	39.1	9.7	52	6.02	36.4	2.33
C488401		2.69	0.28	5.04	28.9	600	1.89	0.12	3.12	4.02	35.5	9.2	57	5.68	30.5	2.18
C488402		2.69	0.36	5.86	35.4	470	2.5	0.23	2.41	3.72	42.7	11.5	64	7.04	37.6	2.53

Comments: Interference: Ca>10% on ICP-MS As,ICP-AES results shown. REE's may not be totally soluble in MS61 method.

ALS Chemex

EXCELLENCE IN ANALYTICAL CHEMISTRY

ALS Canada Ltd.

212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO - RICH

Finalized Date: 2-OCT-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07099393

Sample Description	Method	ME-MS61	ME-MS61	ME-MS61	Hg-CV41	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61
	Analyte	Ga	Ge	Hf	Hg	In	K	La	Li	Mg	Mn	Mo	Na	Nb	Ni	P
	Units	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	%	ppm	ppm	%	ppm	ppm	ppm
	LOR	0.05	0.05	0.1	0.01	0.005	0.01	0.5	0.2	0.01	5	0.05	0.01	0.1	0.2	10
C488391		3.35	0.12	0.7	0.05	0.011	0.49	8.3	9.2	0.09	39	44.5	0.03	2.8	148.5	180
C488392		2.98	0.11	0.6	0.05	0.01	0.45	7.9	14.6	0.08	39	46	0.03	2.4	147.5	220
C488393		2.64	0.09	0.5	0.07	0.011	0.54	7.3	10.2	0.09	37	42.9	0.03	2.3	150.5	290
C488394		4.28	0.14	0.8	0.08	0.018	0.58	7.5	12.9	0.11	57	48.7	0.03	3.1	186	240
C488395		6.43	0.18	1.3	0.13	0.021	0.69	9.2	20.6	0.14	64	64.7	0.03	4.5	262	260
C488396		11.4	1.15	1.4	0.15	0.195	1.08	16.2	9.3	0.21	110	237	0.04	5.1	6460	970
C488397		2.45	0.1	0.3	0.02	0.01	0.22	9.4	2.4	0.42	196	8.75	0.07	1.1	55.3	340
C488398		4.92	0.1	0.7	0.05	0.019	0.73	9.5	4.5	9.11	188	14.2	0.03	3.4	56.4	360
C488399		11.65	0.18	1.8	0.12	0.052	1.51	25	9.3	0.43	134	35.3	0.05	6.8	130	720
C488400		12.9	0.21	2	0.12	0.055	1.64	22.3	10	0.64	150	33	0.05	7.7	124.5	260
C488401		12.35	0.18	1.9	0.10	0.044	1.67	19.5	8.5	0.45	119	29.3	0.05	7.1	107.5	210
C488402		15.2	0.2	2.3	0.11	0.045	1.92	23.1	10	0.56	122	34.3	0.05	8.5	128.5	310

Comments: Interference: Ca>10% on ICP-MS As,ICP-AES results shown. REE's may not be totally soluble in MS61 method.

ALS Chemex

EXCELLENCE IN ANALYTICAL CHEMISTRY

ALS Canada Ltd.

212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO - RICH

Finalized Date: 2-OCT-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07099393

Sample Description	Method	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61
	Analyte	Pb	Rb	Re	S	Sb	Sc	Se	Sn	Sr	Ta	Te	Th	Ti	Tl	U
	Units	ppm	ppm	ppm	%	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm
	LOR	0.5	0.1	0.002	0.01	0.05	0.1	1	0.2	0.2	0.05	0.05	0.2	0.005	0.02	0.1
C488391		5.5	29.6	0.04	1.02	5.18	3.5	10	0.5	37.2	0.15	0.08	1.8	0.067	2.21	8.7
C488392		4.8	26	0.034	0.94	4.1	3.1	9	0.6	38.1	0.13	0.07	1.6	0.06	1.85	8.2
C488393		4.2	23.5	0.028	1.21	5.05	2.9	9	0.5	33.2	0.13	0.08	1.3	0.073	2.24	7.6
C488394		6.1	34.7	0.052	1.5	7.09	4.3	14	0.6	41.9	0.17	0.13	1.8	0.082	3.18	10
C488395		7.3	42	0.093	1.97	10.55	6	23	0.9	43.3	0.27	0.21	2.8	0.116	4.54	12.1
C488396		10.6	63.7	3.12	4.8	20.6	6.8	250	2.4	80.8	0.33	3.27	2.8	0.137	29.8	12
C488397		2.4	16	0.023	0.47	1.97	2.4	9	0.3	896	0.06	0.05	0.7	0.03	0.93	1.8
C488398		10	42.4	0.019	1	3.3	3.7	9	0.7	78	0.21	<0.05	2.6	0.088	1.55	3
C488399		10.3	97.6	0.032	2.2	8.08	9	19	1.7	120.5	0.43	0.08	5.7	0.199	3.9	7
C488400		11.1	108	0.033	2.62	8.61	9.9	21	1.7	116.5	0.5	0.07	6.5	0.229	4.45	6
C488401		10.5	103.5	0.024	2.47	7.51	9.5	12	1.6	109	0.46	0.08	5.7	0.222	3.99	5.2
C488402		12.6	124.5	0.027	2.85	7.94	11.6	14	2	90.1	0.54	0.07	7	0.253	4.85	6

Comments: Interference: Ca>10% on ICP-MS As,ICP-AES results shown. REE's may not be totally soluble in MS61 method.

ALS Chemex
EXCELLENCE IN ANALYTICAL CHEMISTRY
ALS Canada Ltd.
212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: STRATEGIC METALS LTD.
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO - RICH

Finalized Date: 2-OCT-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07099393

Sample Description	Method / Analyte / Units / LOR	ME-MS61 V ppm 1	ME-MS61 W ppm 0.1	ME-MS61 Y ppm 0.1	ME-MS61 Zn ppm 2	ME-MS61 Zr ppm 0.5
C488391		278	0.4	14	278	27.2
C488392		156	0.4	11.4	252	23.4
C488393		154	0.3	9.1	253	21.9
C488394		522	0.5	17	535	32.5
C488395		860	0.7	20.9	847	48.4
C488396		565	0.9	23.5	2880	50
C488397		152	0.1	44.6	116	11.7
C488398		234	0.4	6.7	125	25.8
C488399		661	0.7	16.6	392	59.4
C488400		729	0.8	17.3	377	65.5
C488401		655	0.8	18.2	354	62.2
C488402		709	0.9	22.5	295	72.4

Comments: Interference: Ca>10% on ICP-MS As,ICP-AES results shown. REE's may not be totally soluble in MS61 method.

ALS Chemex
EXCELLENCE IN ANALYTICAL CHEMISTRY
ALS Canada Ltd.
212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Finalized Date: 3-OCT-2007
Account: MTT

CERTIFICATE VA07099392

Project: NIMO - RICH

P.O. No.: R107-18

This report is for 19 Drill Core samples submitted to our lab in Vancouver, BC, Canada on 31-AUG-2007.

The following have access to data associated with this certificate:

AL ARCHER VANCOUVER OFFICE	DOUG EATON BILL WENGZYNOWSKI	JOAN MARIACHER

SAMPLE PREPARATION

ALS CODE	DESCRIPTION
WEI-21	Received Sample Weight
LOG-22	Sample login - Rcd w/o BarCode
PUL-QC	Pulverizing QC Test
CRU-31	Fine crushing - 70% <2mm
SPL-21	Split sample - riffle splitter
PUL-31	Pulverize split to 85% <75 um

ANALYTICAL PROCEDURES

ALS CODE	DESCRIPTION	
ME-MS61	48 element four acid ICP-MS	
Hg-CV41	Trace Hg - cold vapor/AAS	FIMS

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

This is the Final Report and supersedes any preliminary report with this certificate number. Results apply to samples as submitted. All pages of this report have been checked and approved for release.

Signature:

Lawrence Ng, Laboratory Manager - Vancouver

ALS Chemex

EXCELLENCE IN ANALYTICAL CHEMISTRY

ALS Canada Ltd.

212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO - RICH

Finalized Date: 3-OCT-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07099392

Sample Description	Method	WEI-21	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61
	Analyte	Recvd Wt.	Ag	Al	As	Ba	Be	Bi	Ca	Cd	Ce	Co	Cr	Cs	Cu	Fe
	Units	kg	ppm	%	ppm	ppm	ppm	ppm	%	ppm	ppm	ppm	ppm	ppm	ppm	%
	LOR	0.02	0.01	0.01	0.2	10	0.05	0.01	0.01	0.02	0.01	0.1	1	0.05	0.2	0.01
C488351		2.12	0.31	1.82	14.4	470	1.19	0.06	0.5	2.2	15.5	5.5	34	2.17	35.2	1.44
C488352		2.23	0.19	1.72	13.8	520	1.26	0.11	0.07	1.7	14.4	4.6	45	2.24	29.2	1.15
C488353		1.76	0.15	1.45	10.6	590	1.14	0.04	0.04	1.35	12.4	3.9	44	1.89	28.9	1.28
C488354		1.69	0.13	1.4	10.5	600	1.12	0.06	0.59	0.83	13.35	4.1	38	1.71	27.8	1.17
C488355		1.38	0.16	1.72	15.2	350	1.16	0.05	0.14	1.02	14.95	5.1	39	2.04	36.4	1.42
C488356		0.95	0.22	1.77	21.4	400	1.14	0.05	0.08	1.68	15.6	6	34	2.14	45.3	1.83
C488357		0.91	0.2	1.68	13.9	570	1.02	0.08	0.06	2.99	14.6	4.6	43	2.08	30.4	1.46
C488358		0.66	0.25	1.66	14.6	320	0.94	0.04	0.09	4.05	14.75	4.5	37	2.19	33.3	1.6
C488359		0.59	0.38	2.41	39.6	370	1.13	0.1	0.46	3.33	21.2	7.4	47	2.77	62.6	2.4
C488361		0.53	0.82	8.87	81.1	130	5.16	0.27	0.47	7.48	75.1	19.5	121	15.35	99.2	4.93
C488362		1.36	0.01	0.14	<5	40	0.13	0.02	20.6	0.11	2.17	1.6	2	0.15	2.5	0.44
C488363		0.72	0.04	0.65	<5	2960	0.55	<0.01	35.2	0.64	11.3	2	7	0.68	6.4	0.29
C488364		0.92	0.36	4.63	30.9	310	1.96	0.21	7.76	3.57	39.4	8.8	59	6.05	38.2	2.22
C488365		0.80	0.21	4.23	21.3	320	1.49	0.08	5.35	2.07	35.2	7.7	53	4.83	28.2	1.84
C488366		1.83	0.27	4.65	24.1	280	1.6	0.12	2.54	5.5	32.4	9	53	6.03	34.3	2.32
C488367		1.91	0.33	4.67	18	720	1.65	0.17	3.05	4.11	38.1	9.3	58	6.39	33.4	1.96
C488368		1.82	0.28	5.47	17	420	2.07	0.14	3.25	3.42	40.1	10.2	61	6.8	32.4	2.44
C488369		2.81	0.28	4.8	13.7	580	1.95	0.11	2.02	3.05	33.2	9.1	56	6.08	32.2	2.28
C488370		2.65	0.25	3.98	15.5	360	1.52	0.1	3.31	3.06	35	7.7	60	4.6	33	2.04

Comments: Interference: Ca>10% on ICP-MS As,ICP-AES results shown. REE's may not be totally soluble in MS61 method.

ALS Chemex

EXCELLENCE IN ANALYTICAL CHEMISTRY

ALS Canada Ltd.

212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO - RICH

Finalized Date: 3-OCT-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07099392

Sample Description	Method	ME-MS61	ME-MS61	ME-MS61	Hg-CV41	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61
	Analyte	Ga	Ge	Hf	Hg	In	K	La	Li	Mg	Mn	Mo	Na	Nb	Ni	P
	Units	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	%	ppm	ppm	%	ppm	ppm	ppm
	LOR	0.05	0.05	0.1	0.01	0.005	0.01	0.5	0.2	0.01	5	0.05	0.01	0.1	0.2	10
C488351		4.41	0.14	0.7	0.07	0.015	0.56	9.6	6.4	0.32	112	39.6	0.06	2.9	151	390
C488352		4.2	0.12	0.8	0.06	0.013	0.53	9.4	5.3	0.11	53	42.4	0.04	3.1	149.5	180
C488353		3.55	0.12	0.7	0.05	0.014	0.44	7.6	4.9	0.09	58	44	0.04	2.9	135	160
C488354		3.33	0.13	0.7	0.04	0.01	0.41	9	5	0.21	90	50.4	0.05	2.9	140.5	230
C488355		4.03	0.13	0.8	0.07	0.011	0.55	9.3	5.5	0.12	60	56.8	0.04	3.3	163.5	270
C488356		4.34	0.17	0.9	0.11	0.013	0.57	8.5	5.4	0.12	69	67.2	0.03	3.5	182.5	180
C488357		4.44	0.14	0.9	0.06	0.019	0.52	7.7	6.4	0.11	71	45	0.04	3.4	148	130
C488358		5.2	0.14	0.9	0.07	0.02	0.51	7.5	5.6	0.12	81	46.3	0.04	3.3	164	150
C488359		8.25	0.23	1.4	0.16	0.017	0.77	10.6	6.5	0.16	93	44.5	0.03	5	189	180
C488361		32.7	0.53	3.5	0.23	0.146	3.24	47.7	22	0.7	160	100.5	0.13	14	358	1620
C488362		0.59	0.07	<0.1	<0.01	0.006	0.06	0.7	1.2	12.45	192	0.74	0.01	0.4	5.7	240
C488363		1.79	0.09	0.2	0.02	0.011	0.17	8.2	1.6	0.71	328	4.51	0.13	0.9	20.5	340
C488364		12.95	0.24	1.8	0.11	0.054	1.47	22.5	8.8	1.32	289	38.1	0.1	7	121.5	450
C488365		10.75	0.19	1.7	0.08	0.03	1.35	19.9	8.1	0.54	173	27.9	0.07	6.3	103.5	390
C488366		12.15	0.19	1.8	0.10	0.049	1.48	18.3	8.8	1.32	283	29.8	0.08	7	116.5	290
C488367		12.7	0.15	1.8	0.09	0.047	1.48	20.7	7.8	0.39	103	31.1	0.05	6.3	107	220
C488368		14.5	0.18	2.1	0.11	0.044	1.76	21.8	8.9	0.6	139	28.8	0.12	7.9	106.5	290
C488369		12.25	0.17	1.8	0.10	0.042	1.52	17.7	8.2	0.47	114	34.1	0.06	6.7	130	220
C488370		9.76	0.18	1.8	0.10	0.034	1.25	21	5.9	0.4	110	37.1	0.05	6	139.5	400

Comments: Interference: Ca>10% on ICP-MS As,ICP-AES results shown. REE's may not be totally soluble in MS61 method.

ALS Chemex

EXCELLENCE IN ANALYTICAL CHEMISTRY

ALS Canada Ltd.

212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO - RICH

Finalized Date: 3-OCT-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07099392

Sample Description	Method	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61
	Analyte	Pb	Rb	Re	S	Sb	Sc	Se	Sn	Sr	Ta	Te	Th	Ti	Tl	U
	Units	ppm	ppm	ppm	%	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm
	LOR	0.5	0.1	0.002	0.01	0.05	0.1	1	0.2	0.2	0.05	0.05	0.2	0.005	0.02	0.1
C488351		5.8	34.8	0.041	1.04	8.91	4.5	11	1.1	65	0.15	0.09	1.9	0.076	2.37	8.5
C488352		5.4	34.5	0.052	1	5.31	3.8	9	0.8	35.8	0.18	0.09	2.1	0.076	2.18	7.8
C488353		4.6	28.7	0.038	0.94	3.83	3.5	9	0.6	34.5	0.15	0.11	1.7	0.065	2	8.6
C488354		4.5	26.7	0.04	0.9	2.91	3.3	10	0.6	64	0.14	0.1	1.7	0.063	1.97	9.3
C488355		5.8	33.9	0.04	1.23	3.78	4.1	13	0.9	37.4	0.19	0.09	1.9	0.083	3.11	10.4
C488356		8	35.2	0.058	1.71	6.17	4.5	16	1.1	28.9	0.2	0.09	2.1	0.088	4.67	11.9
C488357		4.8	32.9	0.05	1.1	4.74	4.3	13	0.7	25.5	0.19	0.08	2.2	0.088	2.66	7.6
C488358		5	33.7	0.061	1.23	5.06	4.5	17	0.8	28.2	0.19	0.12	2.1	0.084	3.14	8.3
C488359		9.7	47.2	0.055	2.35	9.41	6.3	34	0.7	65.8	0.33	0.39	3	0.122	5.67	9.8
C488361		23.6	216	0.114	5.33	22.4	18.7	79	3.1	115.5	0.85	0.36	10	0.408	13.9	22.1
C488362		1.8	2.7	<0.002	0.04	0.17	0.5	3	0.2	50.2	<0.05	<0.05	0.3	0.006	0.05	0.9
C488363		1.6	11.5	0.005	0.45	1.36	3.2	6	0.2	414	0.05	<0.05	0.6	0.026	0.59	2.4
C488364		10	97	0.033	2.65	8.48	9.7	26	1.6	254	0.43	0.07	5.5	0.2	4.4	7.7
C488365		9.1	84.5	0.023	2.16	5.47	8.8	18	1.4	174.5	0.41	0.05	5.5	0.192	3.39	5.7
C488366		10.3	99.9	0.03	2.55	7.32	8.8	21	1.6	154	0.46	0.06	5.6	0.214	4.4	5.5
C488367		10.5	87.1	0.031	2.2	6.52	9.2	12	1.6	121.5	0.47	0.08	5.1	0.206	4.33	5.5
C488368		11.6	109.5	0.021	2.73	6.52	10.2	12	1.8	121	0.52	0.07	6.4	0.248	3.94	5.1
C488369		115.5	99.7	0.031	2.48	5.26	9.2	11	1.7	94.4	0.45	0.06	5.5	0.216	4.25	5.6
C488370		9.2	76.4	0.035	2.24	4.55	8.1	10	1.3	124.5	0.39	0.08	5	0.199	3.91	7.3

Comments: Interference: Ca>10% on ICP-MS As,ICP-AES results shown. REE's may not be totally soluble in MS61 method.

ALS Chemex
EXCELLENCE IN ANALYTICAL CHEMISTRY
ALS Canada Ltd.
212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO - RICH

Finalized Date: 3-OCT-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07099392

Sample Description	Method	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61
	Analyte	V	W	Y	Zn	Zr
	Units	ppm	ppm	ppm	ppm	ppm
	LOR	1	0.1	0.1	2	0.5
C488351		462	0.4	25.6	389	29.5
C488352		382	0.4	13	264	29.7
C488353		280	0.3	14.6	201	26.9
C488354		165	0.4	20	154	26.7
C488355		166	0.4	16.2	175	32
C488356		374	0.4	23.7	250	34.8
C488357		624	0.3	19.4	421	33.1
C488358		661	0.4	17.4	518	35.5
C488359		548	0.5	18.9	461	49.8
C488361		2030	1.4	34.3	848	115
C488362		5	0.1	1.1	20	<0.5
C488363		104	0.1	19.4	60	8.9
C488364		677	0.7	27.7	323	65.2
C488365		498	0.6	21.7	161	57.5
C488366		682	0.7	12.7	436	59.7
C488367		640	0.8	16.2	344	60.8
C488368		660	0.8	23.3	290	65.7
C488369		654	0.8	17.3	268	58.3
C488370		688	0.7	24.5	286	58.7

Comments: Interference: Ca>10% on ICP-MS As,ICP-AES results shown. REE's may not be totally soluble in MS61 method.

ALS Chemex
EXCELLENCE IN ANALYTICAL CHEMISTRY
ALS Canada Ltd.
212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Finalized Date: 20-SEP-2007
Account: MTT

CERTIFICATE VA07098783

Project: NIMO

P.O. No.:

This report is for 156 Soil samples submitted to our lab in Vancouver, BC, Canada on 15-AUG-2007.

The following have access to data associated with this certificate:

AL ARCHER VANCOUVER OFFICE	DOUG EATON BILL WENGZYNOWSKI	JOAN MARIACHER

SAMPLE PREPARATION

ALS CODE	DESCRIPTION
WEI-21	Received Sample Weight
LOG-22	Sample login - Rcd w/o BarCode
SCR-41	Screen to -180um and save both

ANALYTICAL PROCEDURES

ALS CODE	DESCRIPTION
ME-MS41	51 anal. aqua regia ICPMS

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

This is the Final Report and supersedes any preliminary report with this certificate number. Results apply to samples as submitted. All pages of this report have been checked and approved for release.

Signature:

Lawrence Ng, Laboratory Manager - Vancouver

ALS Chemex

EXCELLENCE IN ANALYTICAL CHEMISTRY

ALS Canada Ltd.

212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: STRATEGIC METALS LTD.
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO

Finalized Date: 20-SEP-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07098783

Sample Description	Method	WEI-21	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41
	Analyte	Recvd Wt.	Ag	Al	As	Au	B	Ba	Be	Bi	Ca	Cd	Ce	Co	Cr	Cs
	Units	kg	ppm	%	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppm	ppm	ppm
	LOR	0.02	0.01	0.01	0.1	0.2	10	10	0.05	0.01	0.01	0.01	0.02	0.1	1	0.05
CC27939		0.34	2.01	0.56	27.4	<0.2	<10	3090	0.68	0.18	0.97	11.15	24.10	6.6	51	0.81
CC27940		0.34	1.43	0.80	41.9	<0.2	10	3540	0.96	0.19	0.62	14.05	26.60	6.5	61	0.87
CC27941		0.32	1.55	0.76	35.1	<0.2	10	3290	0.88	0.17	0.60	11.75	23.40	4.7	51	0.77
CC27942		0.36	0.60	0.90	18.7	<0.2	<10	5450	0.81	0.20	0.42	4.04	38.60	7.7	23	0.63
CC27943		0.38	0.65	0.86	10.3	<0.2	<10	2970	0.53	0.23	0.20	0.48	48.20	4.5	16	0.56
CC27944		0.26	0.79	1.02	6.4	<0.2	10	2010	0.73	0.21	1.19	0.97	31.90	15.9	18	0.85
CC27945		0.26	0.84	1.07	7.8	<0.2	10	2690	0.77	0.22	1.03	0.71	34.90	10.4	20	0.91
CC27946		0.28	0.55	1.08	5.2	<0.2	<10	2750	0.49	0.19	0.99	0.35	27.60	7.7	18	0.90
CC27947		0.32	1.63	1.01	12.6	<0.2	10	2840	0.79	0.19	0.74	14.65	31.00	8.3	48	1.14
CC27948		0.38	2.23	0.76	43.9	<0.2	10	4800	0.93	0.19	0.75	15.25	23.00	2.6	67	0.84
CC27949		0.38	2.11	0.64	29.3	<0.2	10	4140	0.76	0.17	1.36	16.50	17.80	6.0	63	0.69
CC27950		0.40	4.06	0.83	27.8	<0.2	10	3920	0.96	0.20	1.34	28.40	20.90	2.7	83	1.18
CC27951		0.34	3.14	0.65	60.3	<0.2	10	4720	0.84	0.20	1.67	21.20	18.40	5.4	70	1.12
CC27952		0.34	2.62	1.23	43.4	<0.2	20	1920	1.05	0.17	1.98	75.70	21.80	16.0	58	1.34
CC27953		0.36	2.29	1.63	69.1	<0.2	10	1760	0.78	0.27	0.12	9.41	19.15	9.7	66	2.59
CC27954		0.42	1.38	1.00	61.5	<0.2	10	1000	0.81	0.24	0.03	1.91	19.10	3.4	66	1.99
CC27955		0.38	0.91	1.31	50.5	<0.2	10	1740	0.70	0.25	0.06	3.01	18.90	4.2	75	2.12
CC27956		0.36	0.83	1.58	47.2	<0.2	10	2200	0.64	0.24	0.08	4.11	17.30	4.9	78	1.75
CC27957		0.12	0.38	1.16	3.1	<0.2	<10	2100	0.53	0.15	0.13	1.34	32.70	1.7	31	0.84
CC27958		0.36	0.52	1.14	13.5	<0.2	<10	2740	0.55	0.18	0.18	2.93	31.00	3.3	31	0.77
CC27959		0.20	0.42	0.99	3.6	<0.2	<10	2340	0.45	0.16	0.16	2.26	27.10	2.0	27	0.66
CC27960		0.22	0.58	1.22	15.5	<0.2	<10	2760	0.55	0.18	0.20	2.56	31.20	4.3	32	0.74
CC27961		0.16	0.55	1.30	12.1	<0.2	<10	3540	0.70	0.18	0.19	3.10	34.60	4.2	36	0.82
CC27962		0.34	0.69	1.26	13.9	<0.2	<10	3540	0.60	0.20	0.20	3.96	32.30	6.5	34	0.70
CC27963		0.34	0.76	1.22	14.1	<0.2	<10	3350	0.56	0.18	0.25	3.36	31.60	4.7	33	0.77
CC27964		0.22	0.84	1.09	10.8	<0.2	<10	3800	0.49	0.17	0.31	6.23	32.40	8.1	31	0.64
CC27965		0.20	0.90	0.90	6.4	<0.2	<10	3720	0.46	0.15	0.16	5.31	24.30	1.5	32	0.67
CC27966		0.22	1.88	0.93	5.8	<0.2	<10	3600	0.48	0.14	0.14	4.26	21.90	1.2	37	0.90
CC27967		0.30	1.13	1.22	16.6	<0.2	<10	4400	0.60	0.17	0.23	8.89	30.50	5.6	38	0.86
CC27968		0.20	1.49	1.23	9.8	<0.2	<10	4050	0.50	0.17	0.30	6.46	27.70	5.7	35	0.78
CC27969		0.10	1.62	0.76	82.0	<0.2	<10	980	0.32	0.45	0.03	1.14	22.30	3.4	83	1.49
CC27970		0.14	0.92	1.03	14.7	<0.2	<10	4060	0.63	0.16	0.34	2.89	25.10	2.4	40	0.75
CC27971		0.10	1.12	0.83	3.6	<0.2	<10	4920	0.61	0.17	0.76	6.59	21.80	1.8	45	0.71
CC27972		0.20	2.31	1.09	32.5	<0.2	<10	5640	0.88	0.20	0.47	15.60	26.60	6.6	52	1.26
CC27973		0.26	4.49	1.25	14.7	<0.2	<10	4150	0.79	0.19	0.41	29.40	27.60	5.3	57	1.39
CC27974		0.20	0.31	1.24	7.6	<0.2	<10	1190	0.50	0.18	0.39	5.66	32.60	9.2	21	0.68
CC27975		0.14	0.24	1.16	8.0	<0.2	<10	1080	0.49	0.17	0.50	7.77	28.30	10.6	20	0.69
CC27976		0.14	0.34	1.19	8.4	<0.2	<10	1210	0.53	0.18	0.48	8.17	31.40	9.8	22	0.67
CC27977		0.14	0.40	1.32	17.3	<0.2	<10	1360	0.64	0.20	0.58	13.40	33.40	17.0	21	0.66
CC27978		0.14	0.31	1.25	9.7	<0.2	<10	1060	0.50	0.19	0.38	4.91	30.70	14.5	22	0.71

Comments: Gold determinations by ME-MS41 are semi-quantitative due to the small sample weight used (0.5g).

ALS Chemex

EXCELLENCE IN ANALYTICAL CHEMISTRY

ALS Canada Ltd.

212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO

Finalized Date: 20-SEP-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07098783

Sample Description	Method	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41
	Analyte	Cu	Fe	Ga	Ge	Hf	Hg	In	K	La	Li	Mg	Mn	Mo	Na	Nb
	Units	ppm	%	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	%	ppm	ppm	%	ppm
	LOR	0.2	0.01	0.05	0.05	0.02	0.01	0.005	0.01	0.2	0.1	0.01	5	0.05	0.01	0.05
CC27939		73.5	1.36	2.96	0.10	0.09	0.47	0.031	0.08	15.5	4.0	0.16	154	36.80	<0.01	0.33
CC27940		86.5	1.95	3.77	0.11	0.08	0.31	0.028	0.09	16.3	5.7	0.12	132	47.90	<0.01	0.44
CC27941		81.3	1.91	3.49	0.10	0.06	0.33	0.028	0.08	15.3	5.3	0.11	144	33.70	<0.01	0.46
CC27942		57.8	2.57	2.71	0.10	0.06	0.28	0.040	0.14	22.5	4.3	0.11	184	34.40	<0.01	0.22
CC27943		30.2	3.29	2.51	0.11	0.04	0.14	0.037	0.13	27.3	3.6	0.10	30	10.90	<0.01	0.16
CC27944		33.0	2.76	2.85	0.09	0.11	0.14	0.036	0.11	17.2	6.5	0.21	621	3.46	<0.01	0.22
CC27945		39.3	3.67	3.06	0.11	0.10	0.15	0.039	0.12	19.2	6.9	0.21	267	3.53	<0.01	0.24
CC27946		15.8	2.16	3.19	0.07	0.08	0.14	0.029	0.11	15.8	8.3	0.23	239	2.15	<0.01	0.23
CC27947		80.5	1.48	3.67	0.14	0.12	0.36	0.032	0.13	17.7	7.7	0.21	78	6.49	<0.01	0.55
CC27948		99.9	1.73	3.61	0.11	0.07	0.37	0.030	0.08	15.2	5.3	0.10	60	32.80	<0.01	0.43
CC27949		77.0	1.24	3.06	0.10	0.08	0.35	0.025	0.09	11.8	4.7	0.17	196	23.70	<0.01	0.43
CC27950		114.5	1.30	3.64	0.13	0.11	0.69	0.029	0.10	14.0	5.6	0.15	53	17.90	<0.01	0.52
CC27951		103.0	1.99	3.28	0.15	0.12	0.54	0.032	0.10	12.5	4.7	0.18	134	37.30	<0.01	0.42
CC27952		182.5	1.64	4.93	0.13	0.07	0.29	0.029	0.10	14.6	5.7	0.29	674	51.10	<0.01	0.99
CC27953		114.0	2.75	6.78	0.13	0.04	0.23	0.035	0.13	12.5	7.7	0.17	256	87.10	<0.01	0.63
CC27954		63.6	2.11	5.59	0.14	0.02	0.13	0.025	0.10	14.0	4.2	0.09	53	74.50	<0.01	0.71
CC27955		73.0	2.20	6.69	0.12	0.02	0.12	0.029	0.10	12.6	6.0	0.13	102	53.50	<0.01	0.65
CC27956		67.1	2.57	6.97	0.10	0.02	0.10	0.033	0.11	10.6	10.1	0.22	120	26.60	<0.01	0.67
CC27957		25.2	0.64	4.41	0.05	0.03	0.10	0.025	0.07	18.5	10.3	0.18	31	1.20	<0.01	0.52
CC27958		34.6	1.64	4.49	0.06	0.02	0.11	0.028	0.07	16.9	10.3	0.20	40	2.82	0.02	0.67
CC27959		31.5	0.75	4.14	0.05	<0.02	0.12	0.025	0.06	14.6	9.4	0.17	31	0.97	0.02	0.53
CC27960		33.9	1.91	4.90	0.06	0.02	0.11	0.029	0.07	16.7	10.1	0.21	47	4.65	0.02	0.60
CC27961		44.2	1.34	4.99	0.07	0.03	0.12	0.033	0.07	18.6	11.8	0.25	47	1.75	0.02	0.68
CC27962		42.8	2.13	4.72	0.07	0.04	0.13	0.033	0.08	17.2	11.1	0.26	83	5.75	0.02	0.75
CC27963		39.1	1.83	4.70	0.06	0.03	0.15	0.030	0.08	16.7	10.5	0.24	75	6.29	0.02	0.65
CC27964		49.3	1.68	4.14	0.08	0.05	0.15	0.029	0.09	17.0	10.7	0.28	104	9.78	0.02	0.71
CC27965		44.2	0.50	4.00	0.07	<0.02	0.26	0.024	0.06	13.5	8.1	0.15	24	1.01	0.02	0.60
CC27966		52.0	0.45	4.62	0.06	<0.02	0.55	0.022	0.06	12.4	7.9	0.13	20	0.97	0.02	0.61
CC27967		56.9	1.65	4.56	0.07	0.02	0.24	0.029	0.09	16.6	10.5	0.24	86	15.25	0.02	0.73
CC27968		59.7	1.37	4.39	0.07	0.03	0.29	0.028	0.09	14.7	10.5	0.25	92	10.05	0.02	0.59
CC27969		52.0	2.66	8.78	0.10	<0.02	0.07	0.035	0.11	12.3	3.0	0.07	42	43.90	0.02	1.15
CC27970		46.4	1.18	4.26	0.06	<0.02	0.18	0.024	0.09	14.0	8.9	0.17	46	7.36	0.02	0.65
CC27971		56.9	0.63	3.52	0.09	0.03	0.20	0.027	0.07	12.2	5.5	0.12	19	1.15	0.03	0.49
CC27972		76.6	1.89	4.82	0.08	0.03	0.32	0.032	0.11	14.9	8.3	0.19	137	32.40	0.03	0.71
CC27973		124.0	1.33	4.83	0.10	0.05	0.90	0.042	0.12	15.5	9.8	0.24	82	6.86	0.02	0.81
CC27974		29.8	2.55	4.21	0.07	0.03	0.08	0.033	0.06	16.3	12.1	0.30	130	3.06	0.02	0.51
CC27975		25.8	3.62	3.95	0.06	0.04	0.09	0.030	0.06	14.5	11.4	0.29	168	2.29	0.02	0.50
CC27976		27.9	2.38	3.90	0.06	0.03	0.08	0.031	0.06	16.1	11.6	0.29	373	2.80	0.02	0.47
CC27977		29.2	5.70	4.31	0.07	0.03	0.08	0.039	0.06	16.7	10.8	0.28	537	9.39	0.02	0.51
CC27978		24.0	3.19	4.26	0.07	0.03	0.07	0.032	0.07	15.3	12.1	0.30	359	4.06	0.01	0.52

Comments: Gold determinations by ME-MS41 are semi-quantitative due to the small sample weight used (0.5g).

ALS Chemex
EXCELLENCE IN ANALYTICAL CHEMISTRY
ALS Canada Ltd.
212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: STRATEGIC METALS LTD.
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO

CERTIFICATE OF ANALYSIS VA07098783

Sample Description	Method	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41
	Analyte	Ni	P	Pb	Rb	Re	S	Sb	Sc	Se	Sn	Sr	Ta	Te	Th	Ti
	Units	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%
	LOR	0.2	10	0.2	0.1	0.001	0.01	0.05	0.1	0.2	0.2	0.2	0.01	0.01	0.2	0.005
CC27939		88.6	1110	10.7	8.9	0.020	0.09	10.60	3.3	6.8	0.8	160.5	0.01	0.15	1.2	0.010
CC27940		145.0	1140	13.1	11.6	0.010	0.06	16.60	4.1	7.0	0.8	129.5	0.01	0.17	2.6	0.012
CC27941		126.5	1080	13.6	11.4	0.016	0.10	11.85	3.6	7.7	0.8	117.5	0.01	0.15	1.6	0.010
CC27942		92.7	850	12.4	12.1	0.007	0.05	5.64	4.8	3.6	0.6	60.2	0.01	0.10	3.2	<0.005
CC27943		25.2	510	19.4	12.7	0.003	0.01	2.30	4.7	2.3	0.4	25.7	<0.01	0.06	6.1	<0.005
CC27944		38.6	740	13.9	13.9	0.004	0.07	1.34	5.2	3.4	0.4	100.5	0.01	0.06	3.5	<0.005
CC27945		39.8	720	15.3	14.4	0.004	0.08	1.53	5.8	3.7	0.4	78.2	0.01	0.06	3.9	<0.005
CC27946		23.9	560	12.6	15.5	0.004	0.08	0.92	4.2	2.6	0.4	71.7	<0.01	0.05	3.1	<0.005
CC27947		104.0	1530	12.4	12.2	0.026	0.13	7.92	5.4	15.8	0.6	136.5	0.01	0.09	3.5	0.014
CC27948		95.2	1380	13.6	11.4	0.009	0.07	16.70	3.8	7.5	0.8	155.0	0.01	0.17	1.4	0.012
CC27949		106.0	1820	9.8	9.9	0.010	0.10	12.75	3.0	8.4	0.7	232.0	0.01	0.15	1.0	0.014
CC27950		143.0	2470	11.9	12.5	0.013	0.10	15.60	4.9	11.3	0.9	299.0	0.01	0.17	2.0	0.018
CC27951		146.5	1950	12.2	10.2	0.021	0.11	19.20	4.4	15.1	0.8	302.0	0.01	0.17	1.8	0.015
CC27952		221.0	1530	14.8	11.2	0.006	0.11	21.20	2.1	15.7	0.6	151.0	0.01	0.15	0.2	0.028
CC27953		196.0	1240	20.8	25.5	0.004	0.13	40.00	3.7	16.5	0.9	35.2	0.01	0.24	0.4	0.026
CC27954		135.5	580	19.8	21.4	0.004	0.09	38.00	2.6	17.5	0.7	13.0	<0.01	0.26	0.3	0.050
CC27955		117.5	850	20.4	20.7	0.003	0.11	24.30	2.2	16.5	0.8	18.6	<0.01	0.21	0.2	0.032
CC27956		93.3	850	20.7	19.2	0.003	0.11	15.65	1.9	12.4	0.8	25.6	<0.01	0.16	0.2	0.019
CC27957		17.2	440	9.8	9.6	0.004	0.04	1.94	3.3	2.3	0.6	29.0	<0.01	0.06	3.1	0.010
CC27958		32.3	580	12.9	13.7	0.007	0.05	3.38	3.5	2.8	0.7	43.8	<0.01	0.06	4.4	0.010
CC27959		19.4	480	10.6	10.7	0.005	0.05	2.23	2.7	2.4	0.7	33.0	<0.01	0.05	3.1	0.009
CC27960		37.8	640	12.4	15.3	0.005	0.04	3.03	3.6	2.7	0.8	43.5	<0.01	0.06	3.4	0.007
CC27961		41.1	620	12.8	14.6	0.004	0.04	3.89	4.4	3.2	0.8	50.4	<0.01	0.06	4.3	0.010
CC27962		47.2	680	13.3	16.0	0.004	0.05	3.82	4.5	3.2	0.7	52.8	<0.01	0.06	4.6	0.012
CC27963		44.0	630	12.1	15.4	0.006	0.05	3.41	3.9	3.6	0.7	59.1	<0.01	0.06	4.2	0.010
CC27964		72.3	800	9.9	12.6	0.004	0.06	4.77	4.4	5.5	0.6	75.1	<0.01	0.06	4.3	0.017
CC27965		22.0	530	10.3	11.1	0.010	0.08	3.63	2.8	5.9	0.6	46.2	<0.01	0.04	2.6	0.013
CC27966		21.8	450	9.5	11.8	0.018	0.09	3.26	2.4	4.9	0.7	37.2	<0.01	0.03	1.5	0.012
CC27967		75.8	800	10.6	15.5	0.004	0.06	5.02	3.6	3.6	0.8	62.8	<0.01	0.07	2.3	0.015
CC27968		65.8	1040	9.1	14.7	0.006	0.06	3.34	3.4	3.6	0.8	58.5	<0.01	0.06	2.0	0.012
CC27969		56.5	510	31.9	17.2	0.003	0.22	22.90	2.1	18.3	1.3	30.6	<0.01	0.29	0.9	0.046
CC27970		42.8	1070	9.3	14.6	0.007	0.06	3.75	2.5	2.8	0.7	93.7	<0.01	0.07	1.2	0.013
CC27971		65.8	1830	9.9	11.0	0.015	0.11	5.16	3.3	12.7	0.8	208.0	<0.01	0.08	2.3	0.013
CC27972		137.0	1200	11.6	18.1	0.007	0.06	12.35	5.2	6.4	1.0	118.5	<0.01	0.12	3.6	0.018
CC27973		178.5	940	13.2	17.7	0.013	0.08	13.45	7.4	9.5	0.9	103.5	<0.01	0.11	3.8	0.016
CC27974		33.9	720	11.5	13.2	0.007	0.07	1.22	3.6	4.7	0.5	40.0	<0.01	0.05	3.5	0.006
CC27975		36.3	720	10.7	13.8	0.007	0.10	1.03	3.6	4.8	0.5	46.0	<0.01	0.05	3.5	0.006
CC27976		33.8	800	11.6	15.6	0.006	0.08	1.09	3.3	4.8	0.5	45.0	<0.01	0.04	3.1	0.006
CC27977		41.6	980	12.8	17.4	0.007	0.09	1.59	3.7	6.4	0.5	57.4	<0.01	0.06	2.9	<0.005
CC27978		32.1	740	11.5	16.2	0.005	0.07	1.14	3.5	5.0	0.5	37.6	<0.01	0.04	3.5	0.006

Comments: Gold determinations by ME-MS41 are semi-quantitative due to the small sample weight used (0.5g).

ALS Chemex

EXCELLENCE IN ANALYTICAL CHEMISTRY

ALS Canada Ltd.

212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO

Finalized Date: 20-SEP-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07098783

Method	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41
Analyte	Tl	U	V	W	Y	Zn	Zr
Units	ppm	ppm	ppm	ppm	ppm	ppm	ppm
Sample Description LOR	0.02	0.05	1	0.05	0.05	2	0.5
CC27939	1.17	8.78	515	0.36	25.80	556	2.7
CC27940	1.02	13.80	767	0.36	30.70	692	2.7
CC27941	1.11	13.25	722	0.35	30.00	524	1.6
CC27942	0.60	4.93	260	0.20	27.50	547	1.0
CC27943	0.20	1.86	71	<0.05	12.40	162	1.4
CC27944	0.17	1.80	55	0.07	17.75	171	2.4
CC27945	0.19	2.20	61	0.06	20.10	144	2.3
CC27946	0.21	1.81	61	0.05	10.85	114	2.0
CC27947	0.92	5.80	436	0.17	25.50	1085	4.3
CC27948	1.13	11.85	758	0.40	32.80	558	1.7
CC27949	0.94	9.21	582	0.27	24.40	804	2.5
CC27950	1.46	12.15	738	0.28	33.70	1640	3.8
CC27951	1.01	10.15	777	0.35	29.70	1145	4.3
CC27952	3.08	5.19	1375	0.29	48.20	4310	1.0
CC27953	7.38	15.55	1510	0.38	20.20	1165	0.5
CC27954	4.86	8.94	1835	0.48	9.16	537	<0.5
CC27955	3.97	8.44	1735	0.35	11.50	568	<0.5
CC27956	2.74	6.32	1370	0.24	10.55	645	<0.5
CC27957	0.47	1.86	250	0.09	9.63	90	0.7
CC27958	0.47	3.25	277	0.16	12.95	174	1.0
CC27959	0.42	2.30	205	0.09	9.55	99	0.5
CC27960	0.41	3.23	266	0.16	12.90	187	0.8
CC27961	0.48	3.27	327	0.14	16.90	225	1.9
CC27962	0.42	3.58	278	0.27	16.30	257	2.4
CC27963	0.47	3.41	285	0.10	14.40	211	1.4
CC27964	0.43	3.68	240	0.11	16.35	350	3.3
CC27965	0.58	3.27	312	0.11	11.30	160	0.5
CC27966	1.15	3.40	374	0.15	11.10	143	0.5
CC27967	0.69	4.42	380	0.18	19.60	469	0.8
CC27968	0.73	4.43	243	0.15	19.20	315	1.0
CC27969	2.84	3.13	1075	0.40	7.75	283	<0.5
CC27970	0.54	4.27	359	0.17	15.65	303	<0.5
CC27971	0.52	4.16	206	0.20	18.45	410	1.7
CC27972	1.07	7.54	577	0.28	30.50	995	2.0
CC27973	1.68	8.96	591	0.27	34.30	1920	3.0
CC27974	0.24	3.36	61	0.10	13.25	174	1.1
CC27975	0.22	2.99	48	0.08	12.45	172	1.5
CC27976	0.22	3.26	56	0.13	13.45	175	1.1
CC27977	0.25	3.54	76	0.11	18.10	222	1.5
CC27978	0.24	2.93	60	0.09	12.10	176	1.2

Comments: Gold determinations by ME-MS41 are semi-quantitative due to the small sample weight used (0.5g).

ALS Chemex
EXCELLENCE IN ANALYTICAL CHEMISTRY
ALS Canada Ltd.
212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: STRATEGIC METALS LTD.
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO

Finalized Date: 20-SEP-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07098783

Sample Description	Method	WEI-21	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41
	Analyte	Recvd Wt.	Ag	Al	As	Au	B	Ba	Be	Bi	Ca	Cd	Ce	Co	Cr	Cs
	Units	kg	ppm	%	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppm	ppm	ppm
	LOR	0.02	0.01	0.01	0.1	0.2	10	10	0.05	0.01	0.01	0.01	0.02	0.1	1	0.05
CC27979		0.18	0.37	1.27	12.3	<0.2	<10	1290	0.62	0.19	0.38	8.12	33.50	16.6	22	0.73
CC27980		0.16	0.30	1.10	7.6	<0.2	<10	1100	0.47	0.17	0.37	6.09	32.70	5.6	21	0.65
CC27981		0.20	0.34	1.19	8.4	<0.2	<10	1230	0.57	0.19	0.41	9.42	33.70	8.3	21	0.71
CC27982		0.14	0.38	1.16	18.1	<0.2	<10	1250	0.56	0.19	0.62	9.11	33.30	22.6	20	0.65
CC27983		0.12	0.37	1.14	13.1	<0.2	<10	1270	0.59	0.19	0.49	8.04	33.30	10.3	21	0.65
CC27984		0.22	0.30	1.14	7.3	<0.2	<10	1310	0.60	0.17	0.50	6.07	32.40	5.7	20	0.70
CC27985		0.14	0.45	1.14	22.2	<0.2	<10	1310	0.63	0.20	0.67	19.65	33.70	23.5	19	0.66
CC27986		0.20	0.31	1.10	8.3	<0.2	<10	1260	0.55	0.17	0.43	9.14	33.80	8.2	20	0.66
CC27987		0.12	0.38	1.12	13.4	<0.2	<10	1360	0.62	0.19	0.72	13.40	36.40	12.0	20	0.65
CC27988		0.10	0.39	1.23	9.3	<0.2	<10	1290	0.54	0.17	0.53	9.46	30.60	4.6	22	0.71
CC27989		0.10	0.31	1.23	7.9	<0.2	<10	1420	0.62	0.18	0.43	9.23	34.60	8.2	22	0.67
CC27990		0.12	0.34	1.22	10.0	<0.2	<10	1450	0.67	0.19	0.56	16.95	36.70	20.8	22	0.68
CC27991		0.22	3.11	1.24	38.3	<0.2	<10	970	0.50	0.28	0.12	1.06	26.50	2.4	32	1.09
CC27992		0.06	2.29	0.60	9.4	<0.2	<10	770	0.37	0.11	0.13	2.09	11.15	0.9	13	0.93
CC27993		0.04	0.59	0.47	35.8	<0.2	<10	350	0.21	0.19	0.14	1.09	9.17	1.9	12	0.64
CC27994		0.18	0.25	0.85	5.9	<0.2	<10	150	0.43	0.15	2.49	0.67	38.20	6.5	11	0.89
CC27995		0.04	0.11	0.68	7.7	<0.2	<10	240	0.37	0.13	6.41	1.29	29.00	8.7	9	0.63
CC27996		0.08	0.32	0.98	4.9	<0.2	<10	190	0.59	0.19	1.58	1.36	39.10	6.7	14	1.05
CC27997		0.08	0.28	0.92	5.4	<0.2	<10	190	0.50	0.17	2.21	1.06	36.80	6.7	12	0.91
CC27998		0.14	0.16	0.72	7.4	<0.2	<10	290	0.44	0.14	4.64	0.74	30.70	7.9	10	0.68
CC27999		0.18	0.32	0.82	9.5	<0.2	<10	390	0.49	0.17	4.84	1.01	32.80	9.3	12	0.77
CC28000		0.20	0.21	0.77	7.1	<0.2	<10	330	0.45	0.14	4.87	0.81	32.60	7.5	11	0.75
CC29810		0.14	0.81	1.24	6.2	<0.2	10	360	0.84	0.13	3.04	4.50	30.00	7.5	24	1.14
CC29811		0.06	0.92	1.24	9.1	<0.2	10	400	0.87	0.12	2.09	3.83	29.90	5.7	24	1.10
CC29812		0.14	0.30	0.97	8.2	<0.2	10	420	0.71	0.14	1.51	1.93	29.00	7.4	17	0.67
CC29813		0.08	0.79	0.74	5.7	<0.2	<10	1020	0.62	0.15	2.31	3.02	22.20	4.9	13	0.72
CC29814		0.14	0.42	0.99	5.9	<0.2	10	1070	0.66	0.15	1.60	1.61	29.70	5.9	18	0.70
CC29815		0.24	0.58	0.83	11.1	<0.2	10	2660	0.64	0.20	1.46	1.83	25.10	12.0	17	0.72
CC29816		0.16	0.59	0.98	8.1	<0.2	10	2210	0.62	0.16	1.66	2.43	27.60	9.1	20	0.86
CC29817		0.22	0.51	0.96	9.3	<0.2	10	2340	0.67	0.16	1.44	2.06	26.20	8.9	20	0.86
CC29818		0.18	0.56	0.99	8.8	<0.2	10	2360	0.64	0.16	1.42	2.37	26.60	9.7	19	0.82
CC29819		0.14	0.65	0.99	7.5	<0.2	10	2150	0.60	0.15	1.42	1.76	25.70	7.1	18	0.69
CC29820		0.14	0.52	0.92	6.9	<0.2	10	2090	0.58	0.14	1.28	1.95	23.30	6.9	18	0.70
CC29821		0.10	0.26	0.99	10.3	<0.2	10	540	0.69	0.17	1.23	0.86	19.40	26.2	19	0.77
CC29822		0.28	0.18	0.86	16.1	<0.2	10	840	0.68	0.15	1.16	0.82	18.90	29.3	17	0.73
CC29823		0.28	0.37	1.08	17.7	<0.2	10	800	0.90	0.18	1.30	1.23	21.10	41.8	22	0.78
CC29824		0.16	0.30	1.08	13.5	<0.2	10	680	0.81	0.18	1.16	0.97	21.20	26.5	21	0.83
CC29825		0.10	0.30	1.01	12.8	<0.2	10	630	0.79	0.17	1.22	1.10	19.20	31.3	21	0.74
CC29826		0.18	0.27	1.02	14.8	<0.2	10	750	0.80	0.17	1.18	0.98	20.20	27.0	21	0.80
CC29827		0.16	0.34	0.96	11.8	<0.2	10	520	0.77	0.17	1.54	1.29	19.40	28.4	19	0.66

Comments: Gold determinations by ME-MS41 are semi-quantitative due to the small sample weight used (0.5g).

ALS Chemex

EXCELLENCE IN ANALYTICAL CHEMISTRY

ALS Canada Ltd.

212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO

Finalized Date: 20-SEP-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07098783

Sample Description	Method	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41
	Analyte	Cu	Fe	Ga	Ge	Hf	Hg	In	K	La	Li	Mg	Mn	Mo	Na	Nb
	Units	ppm	%	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	%	ppm	ppm	%	ppm
	LOR	0.2	0.01	0.05	0.05	0.02	0.01	0.005	0.01	0.2	0.1	0.01	5	0.05	0.01	0.05
CC27979		26.7	3.31	4.19	0.07	0.03	0.09	0.036	0.06	16.9	11.9	0.27	401	2.81	0.02	0.45
CC27980		28.4	1.90	3.74	0.07	0.03	0.07	0.029	0.06	17.0	11.5	0.28	97	2.04	0.02	0.45
CC27981		33.1	2.32	4.06	0.07	0.03	0.07	0.033	0.06	17.1	12.4	0.29	163	2.67	0.02	0.50
CC27982		28.1	4.93	3.72	0.07	0.04	0.08	0.037	0.06	16.1	10.0	0.27	844	9.28	0.02	0.46
CC27983		31.0	3.04	3.78	0.07	0.03	0.08	0.035	0.06	16.8	11.0	0.26	287	4.22	0.02	0.45
CC27984		29.4	1.97	3.73	0.07	0.03	0.08	0.032	0.05	16.5	10.9	0.25	92	1.59	0.01	0.40
CC27985		28.1	7.15	3.38	0.08	0.04	0.09	0.036	0.05	16.7	8.5	0.23	824	6.73	0.02	0.44
CC27986		27.7	2.30	3.58	0.06	0.03	0.07	0.031	0.06	17.4	10.9	0.26	160	2.01	0.02	0.39
CC27987		33.4	4.65	3.46	0.08	0.04	0.09	0.039	0.06	18.4	9.5	0.25	322	3.95	0.02	0.44
CC27988		31.9	1.87	3.86	0.07	0.03	0.12	0.034	0.06	15.9	11.7	0.25	53	1.69	0.02	0.43
CC27989		32.5	2.24	3.97	0.07	0.03	0.10	0.035	0.06	17.7	11.3	0.26	161	2.02	0.02	0.43
CC27990		31.3	3.05	3.93	0.07	0.04	0.09	0.038	0.07	18.5	11.3	0.28	840	2.24	0.02	0.40
CC27991		66.8	1.73	4.88	0.13	0.02	0.56	0.053	0.11	13.5	6.1	0.17	47	36.10	0.01	0.54
CC27992		79.2	0.91	2.09	0.10	<0.02	0.34	0.029	0.06	6.9	0.6	0.03	20	12.55	0.02	0.18
CC27993		24.1	1.50	3.60	0.06	0.03	0.09	0.023	0.12	5.6	2.0	0.04	50	43.90	0.02	0.45
CC27994		17.1	1.75	2.33	0.09	0.12	0.05	0.017	0.06	19.6	24.6	1.65	137	1.82	0.01	0.14
CC27995		15.7	1.81	1.81	0.09	0.19	0.03	0.017	0.06	15.3	20.0	3.83	492	2.45	0.02	0.09
CC27996		24.1	1.71	2.59	0.08	0.17	0.08	0.021	0.07	20.1	25.2	1.03	179	1.19	0.01	0.20
CC27997		22.0	1.74	2.46	0.08	0.15	0.08	0.019	0.06	18.9	25.1	1.28	174	1.38	0.01	0.16
CC27998		22.7	1.89	1.92	0.08	0.20	0.04	0.018	0.06	16.4	21.7	3.38	225	2.48	0.01	0.07
CC27999		38.3	2.62	2.25	0.10	0.21	0.08	0.023	0.08	17.7	22.9	2.61	244	3.41	0.01	0.11
CC28000		23.2	1.96	2.06	0.08	0.15	0.05	0.019	0.07	17.3	22.8	2.97	207	2.40	0.01	0.10
CC29810		54.9	1.58	3.81	0.09	0.15	0.25	0.026	0.15	17.7	20.4	1.27	267	2.07	0.01	0.48
CC29811		57.7	1.50	3.87	0.09	0.16	0.20	0.027	0.12	17.8	23.7	1.03	145	2.11	0.01	0.51
CC29812		30.8	1.92	2.89	0.08	0.11	0.10	0.025	0.12	15.2	11.5	0.57	240	2.16	0.01	0.30
CC29813		69.6	1.63	2.16	0.08	0.09	0.24	0.025	0.06	14.5	7.5	0.35	119	1.15	0.01	0.27
CC29814		37.7	1.61	2.86	0.08	0.11	0.16	0.025	0.11	16.4	10.5	0.55	82	1.42	0.01	0.34
CC29815		50.0	3.41	2.39	0.09	0.13	0.11	0.034	0.14	13.7	7.6	0.65	331	4.97	<0.01	0.19
CC29816		42.7	2.13	2.79	0.08	0.11	0.16	0.029	0.15	15.4	9.5	0.64	237	3.54	<0.01	0.28
CC29817		42.8	2.23	2.87	0.08	0.11	0.12	0.028	0.15	14.6	8.9	0.57	191	5.92	<0.01	0.24
CC29818		45.3	2.26	2.82	0.08	0.11	0.15	0.029	0.14	14.8	9.9	0.51	246	4.61	<0.01	0.31
CC29819		43.7	1.83	2.79	0.07	0.12	0.17	0.027	0.11	14.5	10.6	0.44	144	2.85	<0.01	0.32
CC29820		37.7	1.71	2.71	0.07	0.11	0.15	0.025	0.10	13.2	10.4	0.47	143	3.27	<0.01	0.29
CC29821		22.5	2.73	2.66	0.07	0.09	0.07	0.033	0.08	10.3	15.5	0.74	776	1.85	0.02	0.36
CC29822		22.8	3.21	2.61	0.09	0.10	0.05	0.031	0.08	10.7	15.1	0.55	756	3.53	0.01	0.17
CC29823		39.9	3.49	3.11	0.09	0.10	0.07	0.035	0.10	12.0	17.9	0.65	1355	4.26	0.02	0.24
CC29824		25.5	3.09	3.04	0.08	0.09	0.08	0.035	0.09	11.7	17.4	0.66	734	2.64	0.02	0.33
CC29825		25.0	2.89	2.85	0.08	0.09	0.08	0.033	0.09	10.5	16.7	0.62	775	2.31	0.02	0.31
CC29826		25.1	3.14	3.00	0.08	0.09	0.07	0.035	0.09	11.2	17.1	0.65	740	3.00	0.02	0.29
CC29827		28.5	2.60	2.64	0.08	0.09	0.08	0.033	0.08	10.7	14.5	0.60	688	1.99	0.01	0.34

Comments: Gold determinations by ME-MS41 are semi-quantitative due to the small sample weight used (0.5g).

ALS Chemex

EXCELLENCE IN ANALYTICAL CHEMISTRY

ALS Canada Ltd.

212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO

CERTIFICATE OF ANALYSIS VA07098783

Sample Description	Method	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41
	Analyte	Ni	P	Pb	Rb	Re	S	Sb	Sc	Se	Sn	Sr	Ta	Te	Th	Ti
	Units	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%
	LOR	0.2	10	0.2	0.1	0.001	0.01	0.05	0.1	0.2	0.2	0.2	0.01	0.01	0.2	0.005
CC27979		35.7	800	12.7	16.3	0.007	0.08	1.20	3.8	5.4	0.5	39.0	<0.01	0.05	3.4	0.005
CC27980		27.8	840	11.3	13.6	0.007	0.07	1.01	3.3	4.6	0.4	39.1	<0.01	0.04	3.5	0.007
CC27981		33.0	750	12.2	14.6	0.008	0.08	1.17	3.7	5.1	0.5	41.3	<0.01	0.05	3.6	0.006
CC27982		33.4	990	12.4	17.2	0.007	0.10	1.52	3.5	6.2	0.4	58.5	<0.01	0.05	2.8	0.005
CC27983		35.2	880	12.4	15.0	0.007	0.08	1.28	3.6	5.6	0.4	49.6	<0.01	0.05	3.3	0.005
CC27984		29.6	750	11.0	13.4	0.008	0.08	1.07	3.3	5.2	0.5	49.2	<0.01	0.04	3.2	0.005
CC27985		41.0	940	11.5	16.3	0.008	0.10	1.41	3.7	7.0	0.4	65.5	<0.01	0.05	3.6	<0.005
CC27986		31.4	850	11.3	14.1	0.006	0.07	1.09	3.3	5.0	0.4	43.4	<0.01	0.04	3.5	0.005
CC27987		37.5	970	12.0	15.0	0.009	0.10	1.48	4.1	7.2	0.4	68.3	<0.01	0.05	3.7	0.005
CC27988		31.7	750	10.3	13.4	0.012	0.12	1.02	3.4	5.8	0.5	50.8	<0.01	0.04	2.8	<0.005
CC27989		30.3	790	12.2	14.3	0.007	0.09	1.09	3.6	5.6	0.5	48.8	<0.01	0.04	3.4	<0.005
CC27990		42.2	860	13.0	17.3	0.007	0.08	1.16	4.1	5.9	0.5	54.9	<0.01	0.05	3.5	0.005
CC27991		25.2	1890	20.6	18.9	0.015	0.12	19.95	3.5	21.3	1.2	104.5	<0.01	0.19	1.3	0.011
CC27992		14.5	1260	11.0	5.7	0.006	0.18	13.70	0.5	17.7	0.6	58.1	<0.01	0.14	<0.2	<0.005
CC27993		15.5	660	15.5	10.5	0.001	0.24	6.55	1.4	7.1	0.9	58.4	<0.01	0.15	1.3	0.010
CC27994		18.2	740	19.5	6.6	0.001	0.03	0.82	1.9	1.2	0.2	38.5	<0.01	0.03	4.5	<0.005
CC27995		19.4	870	88.2	4.6	0.001	0.02	0.95	1.8	1.1	<0.2	108.0	<0.01	0.03	4.8	<0.005
CC27996		20.3	890	40.2	8.9	0.002	0.07	0.75	2.5	1.7	0.2	42.3	<0.01	0.03	4.2	<0.005
CC27997		19.6	880	35.8	7.5	0.002	0.06	0.78	2.3	1.6	0.2	48.6	<0.01	0.03	4.0	<0.005
CC27998		22.7	800	29.8	5.0	0.001	0.03	1.03	2.0	1.3	<0.2	75.4	<0.01	0.03	5.0	<0.005
CC27999		29.4	990	34.2	6.3	0.003	0.05	1.35	2.3	2.2	0.2	86.0	<0.01	0.04	5.2	<0.005
CC28000		22.2	910	30.0	5.7	0.002	0.03	1.02	2.0	1.4	<0.2	72.6	<0.01	0.03	4.7	<0.005
CC29810		42.2	2100	10.2	15.9	0.004	0.11	1.95	3.6	4.1	0.5	115.5	<0.01	0.05	1.9	0.014
CC29811		36.0	1850	11.3	12.3	0.008	0.16	2.38	3.3	4.9	0.7	75.9	0.01	0.06	1.7	0.012
CC29812		32.7	1850	11.0	11.1	0.005	0.06	1.31	2.7	2.7	0.4	53.5	<0.01	0.07	2.5	0.008
CC29813		48.6	1310	11.4	9.4	0.008	0.16	1.11	2.6	5.4	0.4	90.2	0.01	0.07	1.0	0.006
CC29814		32.1	1870	11.0	11.0	0.004	0.10	1.14	2.9	3.7	0.4	60.5	<0.01	0.06	1.9	0.008
CC29815		54.9	1210	13.1	10.6	0.006	0.09	2.37	4.1	3.7	0.6	129.0	<0.01	0.07	3.3	0.005
CC29816		45.5	1870	10.9	13.1	0.008	0.11	1.95	3.6	3.7	0.4	121.5	<0.01	0.07	2.4	0.007
CC29817		48.5	1690	10.6	13.0	0.010	0.09	2.40	3.5	3.7	0.5	124.5	<0.01	0.06	2.7	0.006
CC29818		52.7	1680	10.9	12.9	0.009	0.10	2.24	3.5	3.9	0.5	106.0	<0.01	0.06	2.4	0.007
CC29819		41.2	1470	10.5	10.7	0.009	0.11	1.71	3.3	4.1	0.4	88.2	<0.01	0.06	1.8	0.007
CC29820		37.4	1300	9.3	10.4	0.007	0.11	1.62	3.1	4.0	0.4	83.0	<0.01	0.05	2.0	0.007
CC29821		76.1	880	11.3	9.4	0.005	0.10	0.73	3.7	2.4	0.5	49.8	<0.01	0.05	3.5	0.006
CC29822		73.4	1510	12.6	8.8	0.007	0.08	1.25	3.7	2.2	0.4	62.9	<0.01	0.06	3.5	<0.005
CC29823		104.0	1310	14.3	10.8	0.011	0.10	1.39	4.3	3.2	0.7	75.7	0.01	0.08	3.8	<0.005
CC29824		86.3	1020	13.1	10.4	0.006	0.09	0.92	4.2	2.7	0.6	61.9	0.01	0.07	3.6	0.005
CC29825		89.8	1000	12.6	10.0	0.006	0.10	0.90	4.0	3.0	0.5	61.4	<0.01	0.07	3.3	<0.005
CC29826		78.7	1090	13.6	10.4	0.007	0.09	1.02	4.1	2.5	0.7	63.1	<0.01	0.07	3.6	<0.005
CC29827		76.9	920	12.3	9.0	0.006	0.10	0.84	4.1	3.2	0.6	62.8	<0.01	0.06	3.0	0.005

Comments: Gold determinations by ME-MS41 are semi-quantitative due to the small sample weight used (0.5g).

ALS Chemex
EXCELLENCE IN ANALYTICAL CHEMISTRY
ALS Canada Ltd.
212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO

Finalized Date: 20-SEP-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07098783

Sample Description	Method	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41
	Analyte	Tl	U	V	W	Y	Zn	Zr
	Units	ppm	ppm	ppm	ppm	ppm	ppm	ppm
	LOR	0.02	0.05	1	0.05	0.05	2	0.5
CC27979		0.25	3.08	70	0.08	14.50	186	1.1
CC27980		0.22	2.84	54	0.08	12.60	139	1.1
CC27981		0.23	3.16	59	0.13	13.80	160	1.2
CC27982		0.22	3.47	69	0.12	17.10	190	1.4
CC27983		0.22	3.25	61	0.09	15.70	166	1.3
CC27984		0.22	2.71	53	0.10	13.30	146	1.1
CC27985		0.22	3.15	68	0.11	19.75	239	1.7
CC27986		0.20	2.68	56	0.06	14.40	170	1.1
CC27987		0.20	3.47	55	0.09	19.75	191	1.5
CC27988		0.25	2.62	53	0.06	14.45	155	1.3
CC27989		0.21	2.78	57	0.14	15.25	142	1.2
CC27990		0.22	2.85	54	0.09	17.45	234	1.4
CC27991		3.89	10.10	259	0.34	13.20	53	0.8
CC27992		0.87	5.85	79	0.12	8.77	25	<0.5
CC27993		2.16	1.77	222	0.27	3.61	83	1.4
CC27994		0.10	0.77	20	<0.05	9.16	109	4.5
CC27995		0.12	0.85	18	<0.05	9.15	208	8.2
CC27996		0.16	0.92	23	<0.05	11.90	172	5.3
CC27997		0.13	0.95	21	<0.05	11.20	147	4.9
CC27998		0.08	0.93	19	<0.05	9.78	164	9.0
CC27999		0.09	1.19	24	<0.05	11.30	220	9.3
CC28000		0.09	0.97	21	<0.05	10.20	169	6.5
CC29810		0.24	1.99	96	0.08	17.55	299	4.1
CC29811		0.21	2.88	124	0.17	17.85	248	4.4
CC29812		0.11	1.89	79	0.07	13.90	201	2.8
CC29813		0.14	1.48	36	0.07	15.75	240	2.2
CC29814		0.12	2.03	65	0.06	15.50	155	2.5
CC29815		0.13	1.94	71	0.07	16.40	269	4.2
CC29816		0.18	1.96	87	0.08	17.40	243	2.8
CC29817		0.21	2.33	125	0.10	16.65	270	3.1
CC29818		0.17	2.14	103	0.08	17.20	285	3.0
CC29819		0.24	1.86	92	0.08	15.80	211	2.7
CC29820		0.28	1.86	85	0.08	14.10	207	2.7
CC29821		0.15	1.26	44	0.18	19.00	276	2.2
CC29822		0.11	1.56	59	0.05	17.15	280	2.9
CC29823		0.15	1.89	75	0.06	23.20	368	2.5
CC29824		0.16	1.50	56	0.07	21.00	306	2.4
CC29825		0.16	1.44	51	0.08	21.80	307	2.0
CC29826		0.15	1.38	59	0.06	19.10	288	2.4
CC29827		0.16	1.36	47	0.06	22.40	262	2.2

Comments: Gold determinations by ME-MS41 are semi-quantitative due to the small sample weight used (0.5g).

ALS Chemex

EXCELLENCE IN ANALYTICAL CHEMISTRY

ALS Canada Ltd.

212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO

Finalized Date: 20-SEP-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07098783

Sample Description	Method	WEI-21	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41
	Analyte	Recvd Wt.	Ag	Al	As	Au	B	Ba	Be	Bi	Ca	Cd	Ce	Co	Cr	Cs
	Units	kg	ppm	%	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppm	ppm	ppm
	LOR	0.02	0.01	0.01	0.1	0.2	10	10	0.05	0.01	0.01	0.01	0.02	0.1	1	0.05
CC29828		0.24	0.30	1.05	11.9	<0.2	10	650	0.81	0.16	1.33	1.07	20.40	29.5	21	0.77
CC29829		0.20	0.25	0.97	12.1	<0.2	10	630	0.77	0.17	1.31	1.01	19.30	31.9	18	0.76
CC29830		0.08	0.27	0.95	19.5	<0.2	10	710	0.80	0.17	1.30	1.10	19.70	32.2	18	0.68
CC29831		0.18	0.24	0.93	11.3	<0.2	10	570	0.70	0.15	1.25	0.85	19.05	25.5	18	0.72
CC29832		0.12	0.25	0.99	12.5	<0.2	10	860	0.75	0.16	1.18	0.97	22.40	27.6	20	0.77
CC29833		0.32	0.26	0.98	17.9	<0.2	10	700	0.77	0.16	1.59	1.06	21.60	30.8	20	0.77
CC29834		0.26	0.27	0.92	12.1	<0.2	10	550	0.72	0.16	1.57	0.99	18.70	27.7	19	0.73
CC39667		0.24	0.25	0.94	12.6	<0.2	10	660	0.71	0.15	1.72	0.88	18.80	25.4	18	0.72
CC39668		0.34	0.23	0.93	18.1	<0.2	10	720	0.79	0.16	2.00	1.21	25.00	31.2	20	0.78
CC39669		0.22	0.24	0.96	12.5	<0.2	10	630	0.72	0.15	1.74	0.94	18.90	27.4	19	0.75
CC39670		0.18	0.35	1.08	12.6	<0.2	10	570	0.86	0.18	1.65	1.15	20.40	32.0	22	0.85
CC39671		0.22	0.19	0.74	17.0	<0.2	<10	480	0.65	0.15	1.95	0.72	16.95	20.8	15	0.71
CC39672		0.24	0.26	0.81	13.6	<0.2	<10	430	0.67	0.15	1.70	0.88	16.50	22.9	16	0.65
CC39673		0.20	0.29	0.73	23.4	<0.2	10	430	0.81	0.18	1.21	1.01	20.10	26.0	16	0.84
CC39674		0.26	0.21	0.63	18.9	<0.2	10	380	0.66	0.15	1.50	0.92	17.40	24.5	14	0.77
CC39675		0.30	0.17	0.50	12.1	<0.2	10	320	0.73	0.18	0.68	0.65	21.50	24.3	12	0.96
CC39676		0.20	0.25	0.78	12.6	<0.2	10	430	0.68	0.15	1.60	0.95	16.90	28.3	16	0.67
CC39677		0.30	0.19	0.57	12.2	<0.2	10	350	0.73	0.16	1.43	0.66	20.00	23.4	13	0.83
CC39678		0.22	0.20	0.66	10.6	<0.2	10	410	0.62	0.13	2.00	0.65	15.45	17.9	13	0.64
CC39679		0.22	0.23	0.82	11.4	<0.2	10	470	0.79	0.14	1.55	0.79	18.10	25.8	15	0.70
CC39680		0.26	1.47	0.56	52.5	<0.2	10	670	0.84	0.18	2.06	18.20	23.50	11.1	57	0.49
CC39681		0.26	2.71	0.58	37.3	<0.2	10	770	0.92	0.17	3.08	28.70	21.90	4.7	58	0.48
CC39682		0.40	3.43	0.89	41.7	<0.2	10	800	0.97	0.18	3.50	33.80	20.60	6.6	40	0.68
CC39683		0.36	1.35	1.56	43.3	<0.2	<10	850	1.20	0.22	1.40	15.60	33.70	10.5	41	0.63
CC39684		0.40	0.99	1.30	70.1	<0.2	<10	220	0.79	0.21	0.18	12.80	19.70	8.3	65	1.22
CC39685		0.32	0.58	1.00	157.0	<0.2	<10	140	0.26	0.31	0.04	1.80	13.90	2.9	56	0.95
CC39686		0.40	0.54	0.27	13.7	<0.2	<10	360	0.18	0.13	0.07	0.98	4.88	0.4	11	0.50
CC39687		0.40	1.41	1.16	28.4	<0.2	<10	450	0.34	0.24	0.03	0.69	13.40	3.2	21	0.53
CC39688		0.46	1.09	1.36	32.2	<0.2	<10	440	0.40	0.24	0.03	0.82	17.55	3.4	32	0.76
CC39689		0.22	0.34	0.35	6.5	<0.2	<10	250	0.17	0.16	0.02	0.25	6.43	0.3	11	0.58
CC39690		0.44	0.42	0.32	29.8	<0.2	<10	510	0.34	0.14	0.02	0.48	12.20	0.3	28	0.36
CC39691		0.30	1.80	0.86	47.3	<0.2	10	490	0.58	0.44	0.84	0.45	14.85	1.7	28	0.49
CC39692		0.28	0.30	1.03	35.8	<0.2	<10	420	0.30	0.28	0.04	0.45	14.95	3.2	21	0.46
CC39693		0.38	0.64	1.29	20.6	<0.2	<10	930	0.50	0.21	0.11	0.60	19.35	4.4	23	0.54
CC39694		0.32	0.56	0.68	25.3	<0.2	<10	380	0.29	0.21	0.05	0.74	17.75	3.0	19	0.31
CC39695		0.48	1.33	1.06	108.0	<0.2	<10	1700	0.82	0.18	0.09	5.29	21.00	8.2	24	0.35
CC39696		0.34	0.27	0.51	34.5	<0.2	<10	1320	0.49	0.14	0.19	1.69	10.85	4.6	10	0.45
CC39697		0.30	0.99	1.08	21.8	<0.2	<10	2330	0.65	0.18	1.22	6.06	28.30	9.7	23	0.69
CC39698		0.34	0.95	1.18	13.3	<0.2	<10	2840	0.71	0.15	1.22	5.93	27.90	17.4	24	0.63
CC39699		0.32	0.72	1.35	11.9	<0.2	<10	2020	0.85	0.21	0.17	2.47	43.00	7.0	45	0.67

Comments: Gold determinations by ME-MS41 are semi-quantitative due to the small sample weight used (0.5g).

ALS Chemex

EXCELLENCE IN ANALYTICAL CHEMISTRY

ALS Canada Ltd.

212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: STRATEGIC METALS LTD.
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO

Finalized Date: 20-SEP-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07098783

Sample Description	Method	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41
	Analyte	Cu	Fe	Ga	Ge	Hf	Hg	In	K	La	Li	Mg	Mn	Mo	Na	Nb
	Units	ppm	%	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	%	ppm	ppm	%	ppm
	LOR	0.2	0.01	0.05	0.05	0.02	0.01	0.005	0.01	0.2	0.1	0.01	5	0.05	0.01	0.05
CC29828		24.2	2.84	2.88	0.08	0.08	0.08	0.033	0.09	11.2	17.0	0.73	715	2.12	0.02	0.37
CC29829		22.1	2.78	2.76	0.08	0.09	0.07	0.031	0.08	10.5	16.1	0.73	1005	2.35	0.01	0.34
CC29830		25.3	3.94	2.80	0.10	0.09	0.05	0.034	0.08	11.1	14.8	0.62	1055	4.51	0.01	0.25
CC29831		20.3	2.66	2.69	0.07	0.08	0.06	0.029	0.08	10.5	15.5	0.72	750	2.05	0.01	0.34
CC29832		22.7	2.91	2.77	0.08	0.09	0.07	0.031	0.09	12.2	16.4	0.67	672	2.57	0.01	0.34
CC29833		33.0	3.45	2.86	0.09	0.09	0.06	0.034	0.09	12.2	16.0	0.76	939	3.66	0.02	0.29
CC29834		23.4	2.63	2.65	0.08	0.09	0.08	0.032	0.08	10.3	15.0	0.78	775	2.37	0.02	0.31
CC39667		22.1	2.71	2.70	0.07	0.08	0.06	0.030	0.08	10.6	15.2	0.92	691	2.48	0.01	0.30
CC39668		25.2	3.53	2.87	0.10	0.09	0.06	0.033	0.09	14.3	16.2	1.02	1020	3.91	0.01	0.29
CC39669		21.8	2.77	2.65	0.07	0.08	0.06	0.030	0.08	10.4	15.8	0.91	722	2.42	0.02	0.29
CC39670		26.5	2.88	3.03	0.08	0.09	0.10	0.036	0.09	11.0	17.6	0.86	865	2.19	0.02	0.38
CC39671		20.4	2.92	2.34	0.09	0.08	0.05	0.031	0.06	9.4	12.7	1.06	522	3.06	0.01	0.28
CC39672		21.8	2.55	2.43	0.08	0.07	0.07	0.031	0.07	8.8	13.3	0.91	609	2.20	0.01	0.28
CC39673		25.4	3.45	2.36	0.09	0.09	0.08	0.037	0.08	10.9	12.4	0.61	867	3.09	0.01	0.18
CC39674		21.4	3.24	2.08	0.09	0.08	0.07	0.031	0.06	9.1	10.6	0.76	744	2.51	0.01	0.21
CC39675		22.6	3.07	2.00	0.08	0.12	0.07	0.042	0.08	11.0	8.8	0.34	706	1.81	0.01	0.08
CC39676		26.5	2.64	2.27	0.07	0.08	0.08	0.031	0.07	8.9	12.4	0.84	792	2.03	0.02	0.26
CC39677		22.1	2.99	2.02	0.09	0.09	0.07	0.037	0.07	10.5	9.4	0.69	616	2.39	0.01	0.17
CC39678		18.6	2.41	1.97	0.07	0.07	0.07	0.027	0.06	8.2	11.2	1.14	421	2.02	0.01	0.23
CC39679		20.0	2.62	2.12	0.07	0.08	0.07	0.029	0.07	9.6	15.0	0.84	585	1.80	0.02	0.26
CC39680		83.5	1.71	3.03	0.11	0.11	0.31	0.026	0.06	14.8	3.7	0.14	436	20.60	0.01	0.21
CC39681		101.0	1.28	2.91	0.13	0.14	0.53	0.025	0.06	15.3	3.8	0.57	102	22.00	0.01	0.24
CC39682		98.7	1.69	3.41	0.14	0.13	0.70	0.028	0.07	16.7	6.7	0.76	106	34.70	0.01	0.37
CC39683		49.7	2.57	4.98	0.15	0.12	0.20	0.034	0.07	20.2	11.4	0.35	243	36.20	0.01	0.67
CC39684		59.9	2.24	6.09	0.12	0.02	0.19	0.031	0.09	14.4	9.3	0.14	241	26.40	0.01	0.58
CC39685		41.4	2.65	8.06	0.14	0.02	0.08	0.033	0.05	8.8	2.8	0.08	48	73.20	0.01	0.79
CC39686		32.4	0.74	2.08	0.05	<0.02	0.04	0.017	0.08	2.8	0.4	0.02	7	30.60	<0.01	0.10
CC39687		35.1	2.88	4.36	0.08	0.02	0.12	0.034	0.10	6.8	9.0	0.15	107	39.00	0.01	0.67
CC39688		41.0	2.90	5.47	0.08	0.02	0.08	0.044	0.09	8.9	8.5	0.15	113	45.00	<0.01	0.72
CC39689		23.2	0.53	2.16	<0.05	<0.02	0.03	0.015	0.05	3.0	0.4	0.01	6	16.70	0.01	0.11
CC39690		48.8	1.01	2.46	0.07	0.02	0.08	0.057	0.10	4.1	0.6	0.01	8	55.30	<0.01	0.08
CC39691		57.2	2.20	5.17	0.10	0.05	0.53	0.063	0.16	8.2	4.2	0.10	28	43.70	0.01	0.29
CC39692		24.0	3.32	5.14	0.08	<0.02	0.05	0.036	0.12	8.1	5.0	0.11	79	33.20	0.01	0.75
CC39693		24.0	2.35	4.48	0.07	0.02	0.07	0.030	0.10	11.4	11.3	0.25	101	25.90	<0.01	0.45
CC39694		27.0	2.48	3.18	0.11	<0.02	0.03	0.031	0.16	9.8	5.4	0.12	55	47.70	0.01	0.29
CC39695		65.4	4.22	3.13	0.12	0.04	0.08	0.033	0.11	12.0	7.6	0.15	83	99.60	<0.01	0.28
CC39696		32.1	1.77	1.64	0.08	0.04	0.10	0.024	0.06	6.0	2.3	0.06	95	42.50	<0.01	0.15
CC39697		53.5	1.81	2.97	0.08	0.10	0.28	0.029	0.07	16.8	9.4	0.27	109	10.05	<0.01	0.35
CC39698		41.4	2.52	3.41	0.09	0.10	0.25	0.027	0.06	16.1	10.6	0.33	2880	13.40	<0.01	0.32
CC39699		61.1	2.14	4.45	0.09	0.07	0.24	0.033	0.06	24.6	10.3	0.22	218	9.61	<0.01	0.37

Comments: Gold determinations by ME-MS41 are semi-quantitative due to the small sample weight used (0.5g).

ALS Chemex

EXCELLENCE IN ANALYTICAL CHEMISTRY

ALS Canada Ltd.

212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: STRATEGIC METALS LTD.
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO

Finalized Date: 20-SEP-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07098783

Sample Description	Method	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41
	Analyte	Ni	P	Pb	Rb	Re	S	Sb	Sc	Se	Sn	Sr	Ta	Te	Th	Ti
	Units	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%
	LOR	0.2	10	0.2	0.1	0.001	0.01	0.05	0.1	0.2	0.2	0.2	0.01	0.01	0.2	0.005
CC29828		89.5	1030	12.0	9.9	0.006	0.09	0.82	4.0	2.7	0.6	60.1	0.01	0.06	3.6	0.006
CC29829		84.2	990	11.7	9.5	0.005	0.08	0.83	3.7	2.4	0.6	56.8	<0.01	0.06	3.3	0.006
CC29830		83.1	1490	14.5	8.8	0.008	0.08	1.49	3.9	2.7	0.6	64.0	<0.01	0.08	3.5	0.005
CC29831		73.1	1000	11.3	9.0	0.005	0.08	0.78	3.6	2.1	0.4	52.1	<0.01	0.05	3.4	0.006
CC29832		85.2	1110	11.8	9.7	0.007	0.09	1.07	3.9	2.5	0.6	59.8	<0.01	0.07	4.3	0.007
CC29833		80.4	1740	13.9	9.4	0.007	0.13	1.29	4.0	2.7	0.6	71.2	0.01	0.07	3.7	0.006
CC29834		73.0	960	14.2	9.1	0.005	0.09	0.91	3.8	2.5	0.6	58.6	<0.01	0.06	3.3	0.005
CC39667		69.4	1060	12.1	9.2	0.005	0.08	0.92	3.7	2.4	0.4	59.3	<0.01	0.07	3.2	0.005
CC39668		82.6	1670	14.1	9.1	0.006	0.10	1.41	4.0	2.6	0.6	69.5	<0.01	0.07	4.1	0.006
CC39669		75.9	1060	11.8	9.5	0.005	0.09	0.91	3.7	2.4	0.5	59.8	<0.01	0.06	3.2	0.005
CC39670		82.9	960	14.0	11.1	0.005	0.11	0.85	4.3	3.0	0.6	62.8	0.01	0.07	3.4	0.006
CC39671		60.4	1370	12.7	7.2	0.003	0.14	1.05	3.4	2.2	0.4	56.6	<0.01	0.06	3.4	0.005
CC39672		64.8	900	11.8	7.8	0.003	0.12	0.81	3.6	2.3	0.4	51.3	<0.01	0.06	3.2	<0.005
CC39673		75.9	1070	16.9	8.6	0.004	0.15	1.06	4.1	2.4	0.5	63.7	<0.01	0.07	4.1	<0.005
CC39674		67.6	1140	12.8	7.4	0.002	0.20	0.96	3.6	2.1	0.6	54.9	<0.01	0.06	3.5	<0.005
CC39675		57.4	650	11.8	8.6	0.002	0.08	0.55	4.2	1.5	0.5	66.7	<0.01	0.05	5.1	<0.005
CC39676		71.0	910	11.9	7.6	0.002	0.14	0.75	3.6	2.1	0.5	54.4	<0.01	0.05	3.3	<0.005
CC39677		61.5	890	12.1	7.9	0.002	0.09	0.71	4.0	1.8	0.5	82.5	<0.01	0.05	4.3	<0.005
CC39678		57.1	890	10.1	6.6	0.002	0.11	0.74	3.2	1.9	0.4	52.8	<0.01	0.05	3.0	<0.005
CC39679		87.9	880	11.7	7.9	0.002	0.11	0.71	3.5	2.3	0.4	55.1	<0.01	0.05	3.2	<0.005
CC39680		150.0	1540	12.5	7.6	0.015	0.12	14.35	3.0	9.6	0.6	146.0	0.01	0.17	1.3	0.005
CC39681		212.0	1120	11.3	6.7	0.019	0.12	18.50	3.9	14.8	0.6	193.0	0.01	0.17	1.1	0.006
CC39682		254.0	940	12.1	8.3	0.005	0.09	17.80	4.7	15.4	0.6	168.5	0.01	0.14	1.4	0.009
CC39683		171.5	570	15.8	7.5	0.001	0.07	12.30	5.0	16.5	0.7	55.7	0.01	0.13	2.0	0.008
CC39684		94.0	630	20.4	15.5	<0.001	0.06	31.60	2.3	14.2	0.6	17.9	<0.01	0.20	0.4	0.013
CC39685		399.0	240	26.3	7.6	0.001	0.04	34.80	2.1	21.3	1.0	13.7	<0.01	0.40	1.5	0.017
CC39686		9.7	370	9.2	7.3	0.011	0.17	6.76	1.0	7.5	0.6	69.8	<0.01	0.17	0.6	<0.005
CC39687		13.3	570	14.2	10.7	<0.001	0.22	9.24	2.5	8.2	0.7	48.4	<0.01	0.20	1.4	0.013
CC39688		15.2	820	13.9	10.1	<0.001	0.17	7.94	2.6	6.3	0.8	42.4	<0.01	0.20	1.1	0.013
CC39689		4.1	430	11.1	6.4	0.004	0.09	2.01	1.3	3.5	0.5	21.6	<0.01	0.11	0.5	<0.005
CC39690		5.2	660	9.5	5.7	0.020	0.26	4.48	3.4	4.4	0.4	112.0	<0.01	0.13	0.8	<0.005
CC39691		29.6	940	30.4	11.8	0.013	0.37	5.10	3.9	13.9	1.3	173.5	<0.01	0.34	0.9	<0.005
CC39692		31.0	780	16.8	11.0	<0.001	0.23	4.58	2.0	7.6	0.8	46.3	<0.01	0.16	1.3	0.009
CC39693		26.8	690	15.3	11.5	<0.001	0.09	4.76	2.4	4.3	0.6	45.9	<0.01	0.12	2.2	0.007
CC39694		31.7	860	14.7	9.6	0.001	0.41	6.97	1.9	13.3	0.6	119.5	<0.01	0.23	1.6	0.006
CC39695		84.8	1230	15.1	8.5	<0.001	0.15	36.50	3.6	11.2	0.6	86.3	<0.01	0.19	2.1	<0.005
CC39696		53.3	300	8.8	7.0	0.026	0.06	4.45	2.3	11.8	0.4	62.9	<0.01	0.22	1.7	<0.005
CC39697		64.8	850	10.9	10.3	0.014	0.12	2.91	3.6	5.8	0.4	104.5	0.01	0.06	1.9	0.005
CC39698		65.2	940	10.7	8.5	0.010	0.10	2.99	3.5	6.4	0.4	94.3	<0.01	0.07	1.5	0.006
CC39699		46.0	760	12.3	8.7	0.001	0.05	3.16	3.9	3.8	0.6	23.9	0.01	0.09	1.8	0.006

Comments: Gold determinations by ME-MS41 are semi-quantitative due to the small sample weight used (0.5g).

ALS Chemex

EXCELLENCE IN ANALYTICAL CHEMISTRY

ALS Canada Ltd.

212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO

Finalized Date: 20-SEP-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07098783

Sample Description	Method	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41
	Analyte	Ti	U	V	W	Y	Zn	Zr
	Units	ppm	ppm	ppm	ppm	ppm	ppm	ppm
	LOR	0.02	0.05	1	0.05	0.05	2	0.5
CC29828		0.16	1.47	51	0.13	22.40	301	2.1
CC29829		0.16	1.25	48	0.18	20.10	302	2.2
CC29830		0.13	1.81	73	0.08	19.80	307	2.6
CC29831		0.14	1.26	46	0.06	18.15	264	2.0
CC29832		0.15	1.46	55	0.07	19.85	275	2.3
CC29833		0.15	1.71	63	0.06	21.20	301	2.5
CC29834		0.15	1.29	49	0.06	18.65	262	2.1
CC39667		0.14	1.36	51	0.05	17.20	251	2.0
CC39668		0.13	1.73	70	0.08	20.10	290	2.7
CC39669		0.15	1.34	52	0.09	18.45	283	1.9
CC39670		0.17	1.52	52	0.06	22.50	298	2.2
CC39671		0.11	1.40	51	0.05	15.50	222	2.8
CC39672		0.12	1.22	43	0.05	16.20	238	2.2
CC39673		0.12	1.51	55	0.05	17.75	252	2.7
CC39674		0.12	1.29	46	0.11	15.35	232	2.5
CC39675		0.07	1.07	42	<0.05	12.15	214	3.9
CC39676		0.13	1.21	42	<0.05	16.95	247	2.2
CC39677		0.09	1.35	42	<0.05	14.25	216	3.0
CC39678		0.11	1.19	38	<0.05	14.85	208	2.0
CC39679		0.12	1.20	41	0.05	20.90	280	2.0
CC39680		0.82	8.19	825	0.25	29.50	1395	3.8
CC39681		1.18	10.15	742	0.24	37.30	1885	5.2
CC39682		1.72	5.71	656	0.24	40.10	2790	3.9
CC39683		1.22	3.76	563	0.23	32.10	1240	3.3
CC39684		3.01	4.30	1530	0.31	17.05	1125	<0.5
CC39685		6.11	2.20	1525	0.33	5.04	495	1.5
CC39686		2.31	2.96	135	0.16	3.78	29	<0.5
CC39687		2.32	3.38	239	0.27	4.80	55	<0.5
CC39688		2.72	6.54	378	0.26	6.40	52	<0.5
CC39689		1.41	3.72	81	0.11	2.88	8	<0.5
CC39690		2.29	13.35	152	0.19	6.38	8	0.6
CC39691		4.49	6.92	213	0.44	5.76	82	1.8
CC39692		2.19	1.38	238	0.23	2.82	135	0.5
CC39693		1.20	2.66	217	0.13	3.95	169	1.0
CC39694		3.78	2.57	181	0.21	4.59	172	<0.5
CC39695		1.67	9.50	416	0.25	14.85	642	1.1
CC39696		1.76	4.19	109	0.12	9.22	156	1.5
CC39697		0.53	7.03	216	0.12	21.50	412	3.1
CC39698		0.43	5.49	196	0.12	19.65	390	2.7
CC39699		0.56	4.33	232	0.21	25.90	196	1.7

Comments: Gold determinations by ME-MS41 are semi-quantitative due to the small sample weight used (0.5g).

ALS Chemex

EXCELLENCE IN ANALYTICAL CHEMISTRY

ALS Canada Ltd.

212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO

Finalized Date: 20-SEP-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07098783

Sample Description	Method	WEI-21	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41
	Analyte	Recvd Wt.	Ag	Al	As	Au	B	Ba	Be	Bi	Ca	Cd	Ce	Co	Cr	Cs
	Units	kg	ppm	%	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppm	ppm	ppm
	LOR	0.02	0.01	0.01	0.1	0.2	10	10	0.05	0.01	0.01	0.01	0.02	0.1	1	0.05
CC39700		0.36	0.69	1.26	6.7	<0.2	<10	3630	0.69	0.19	0.46	1.18	29.50	10.9	20	0.66
CC39701		0.36	0.44	1.28	4.9	<0.2	<10	2410	0.41	0.20	0.10	0.30	24.90	6.6	19	0.48
CC39702		0.34	0.91	1.31	8.8	<0.2	<10	6320	0.65	0.20	0.66	1.60	29.80	9.0	23	0.48
CC39703		0.42	0.42	1.21	13.4	<0.2	<10	4950	0.65	0.19	0.36	1.13	29.60	6.5	23	0.47
CC39704		0.40	0.45	0.90	14.5	<0.2	<10	3110	0.61	0.16	0.29	2.03	26.80	5.1	26	0.44
CC39705		0.36	1.72	1.11	23.3	<0.2	<10	1440	0.87	0.21	0.69	13.80	29.90	7.2	46	0.65
CC39706		0.32	1.70	1.18	32.4	<0.2	<10	1110	0.98	0.18	2.13	19.10	26.30	7.7	35	0.55
CC39707		0.38	0.20	2.53	17.7	<0.2	<10	480	0.74	0.21	0.05	0.77	22.00	10.7	33	0.99
CC39708		0.32	0.28	3.00	24.1	<0.2	<10	690	1.04	0.23	0.07	1.09	24.80	14.4	38	1.33
CC39709		0.46	0.27	0.55	13.6	<0.2	<10	740	0.58	0.13	0.17	1.36	16.60	4.7	10	0.66
CC39859		0.22	0.45	0.77	11.5	<0.2	<10	170	0.56	0.19	6.87	1.58	30.30	9.6	18	1.71
CC39860		0.28	0.34	0.81	10.4	<0.2	<10	150	0.48	0.19	5.74	1.13	25.70	9.2	13	1.75
CC39861		0.30	0.39	0.83	12.5	<0.2	<10	170	0.57	0.21	6.46	1.43	23.10	10.7	18	1.47
CC39862		0.16	0.34	0.79	11.6	<0.2	<10	160	0.55	0.21	6.77	1.36	25.10	10.6	16	1.50
CC39863		0.28	0.32	0.73	10.0	<0.2	<10	140	0.51	0.18	6.00	1.08	25.10	9.0	12	1.52
CC39864		0.26	0.33	0.75	10.7	<0.2	<10	160	0.52	0.19	7.31	1.24	24.10	9.8	14	1.45
CC39865		0.26	0.27	0.74	9.3	<0.2	<10	160	0.47	0.18	5.51	1.02	25.50	9.0	12	1.50
CC39866		0.34	0.32	0.76	9.9	<0.2	<10	380	0.49	0.18	6.37	1.20	27.10	10.0	14	1.39
CC39867		0.26	0.32	0.75	10.1	<0.2	<10	230	0.49	0.18	6.24	1.17	33.10	9.4	12	1.56
CC39868		0.18	0.34	0.85	12.3	<0.2	<10	310	0.55	0.22	6.45	1.38	23.70	11.9	22	1.38
CC39869		0.26	0.34	0.77	10.3	<0.2	<10	250	0.54	0.18	6.52	1.12	25.40	9.5	14	1.56
CC39870		0.32	0.44	0.78	10.8	<0.2	<10	580	0.55	0.19	7.01	1.76	23.60	9.9	17	1.52
CC39871		0.26	0.32	0.78	10.6	<0.2	<10	410	0.50	0.19	5.99	1.28	24.50	9.7	12	1.52
CC39872		0.36	0.57	0.71	15.9	<0.2	<10	890	0.52	0.18	6.16	3.73	28.70	8.9	17	1.55
CC39873		0.30	0.47	0.73	13.7	<0.2	<10	680	0.51	0.18	5.63	2.76	23.80	9.3	15	1.54
CC39874		0.28	0.39	0.68	13.2	<0.2	<10	510	0.50	0.18	5.32	3.41	22.20	9.6	13	1.36
CC39875		0.24	0.49	0.73	14.4	<0.2	<10	910	0.53	0.18	6.03	4.75	32.00	9.8	16	1.45
CC39876		0.22	0.55	1.00	18.4	<0.2	<10	810	1.19	0.16	5.08	126.50	24.80	20.0	18	1.47
CC39979		0.10	0.24	0.83	4.1	<0.2	<10	130	0.53	0.16	2.21	1.02	40.40	4.7	12	1.12
CC39980		0.16	0.30	0.89	7.0	<0.2	<10	160	0.59	0.17	1.97	0.87	41.50	7.2	13	1.11
CC39981		0.08	0.26	0.87	6.2	<0.2	<10	160	0.54	0.16	2.13	0.78	42.40	6.7	12	1.05
CC39982		0.16	0.13	0.74	8.4	<0.2	<10	120	0.49	0.15	5.02	0.86	36.90	10.4	10	0.80
CC39983		0.14	0.13	0.75	8.2	<0.2	<10	100	0.51	0.16	4.17	0.66	37.00	8.7	10	0.85
CC39984		0.14	0.17	0.76	5.7	<0.2	<10	140	0.46	0.14	2.38	0.56	41.80	6.0	11	0.94
CC39985		0.22	0.34	0.74	10.7	<0.2	<10	130	0.48	0.18	6.08	1.29	28.20	9.5	11	1.46
CC39986		0.22	0.38	0.81	11.0	<0.2	<10	130	0.54	0.18	6.87	1.30	24.40	9.6	12	1.57

Comments: Gold determinations by ME-MS41 are semi-quantitative due to the small sample weight used (0.5g).

ALS Chemex
EXCELLENCE IN ANALYTICAL CHEMISTRY
ALS Canada Ltd.
212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO

CERTIFICATE OF ANALYSIS VA07098783

Sample Description	Method	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41
	Analyte	Cu	Fe	Ga	Ge	Hf	Hg	In	K	La	Li	Mg	Mn	Mo	Na	Nb
	Units	ppm	%	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	%	ppm	ppm	%	ppm
	LOR	0.2	0.01	0.05	0.05	0.02	0.01	0.005	0.01	0.2	0.1	0.01	5	0.05	0.01	0.05
CC39700		36.6	2.01	3.76	0.07	0.07	0.17	0.028	0.07	16.6	10.4	0.25	346	5.12	<0.01	0.33
CC39701		20.7	2.14	4.09	0.06	0.05	0.08	0.027	0.09	13.5	11.2	0.27	152	2.70	<0.01	0.44
CC39702		31.8	2.08	3.93	0.07	0.07	0.16	0.029	0.08	16.7	9.9	0.27	275	9.90	<0.01	0.38
CC39703		33.5	2.27	3.70	0.07	0.06	0.14	0.028	0.07	16.6	10.2	0.28	142	15.45	<0.01	0.36
CC39704		39.2	1.61	3.21	0.06	0.04	0.16	0.022	0.05	15.8	6.8	0.18	129	19.75	<0.01	0.31
CC39705		68.1	1.83	3.86	0.11	0.09	0.31	0.033	0.07	15.3	9.8	0.28	152	21.80	<0.01	0.40
CC39706		69.6	2.01	3.73	0.13	0.13	0.28	0.027	0.07	18.5	9.1	0.28	171	22.20	0.01	0.53
CC39707		35.8	3.08	5.01	0.07	0.14	0.04	0.038	0.06	11.3	25.1	0.36	174	7.74	0.01	0.79
CC39708		41.2	3.46	6.40	0.08	0.22	0.07	0.047	0.07	13.0	29.8	0.34	211	14.80	0.02	0.91
CC39709		39.3	1.51	1.79	0.08	0.06	0.08	0.024	0.06	8.7	2.8	0.07	56	35.00	0.01	0.14
CC39859		40.4	1.95	2.54	0.12	0.19	0.07	0.024	0.09	16.6	23.6	1.62	194	7.35	0.01	0.09
CC39860		31.2	2.11	2.40	0.11	0.14	0.06	0.024	0.07	13.7	25.3	1.39	181	4.88	0.01	0.08
CC39861		36.7	2.20	2.49	0.11	0.34	0.06	0.026	0.09	12.1	24.9	1.42	240	6.68	0.01	0.06
CC39862		33.9	2.16	2.36	0.11	0.25	0.05	0.026	0.08	13.2	24.6	1.44	224	6.09	0.01	0.07
CC39863		30.6	1.97	2.21	0.10	0.14	0.05	0.022	0.06	13.4	23.7	1.33	178	4.71	0.01	0.08
CC39864		33.0	2.04	2.25	0.10	0.27	0.06	0.024	0.08	12.9	23.0	1.58	219	5.53	0.01	0.08
CC39865		26.2	2.01	2.20	0.10	0.15	0.05	0.022	0.06	13.4	24.1	1.30	188	4.12	0.01	0.06
CC39866		32.7	2.03	2.31	0.10	0.20	0.05	0.024	0.08	14.6	22.5	1.42	221	4.74	0.02	0.06
CC39867		33.6	2.06	2.28	0.10	0.17	0.06	0.025	0.07	17.7	23.7	1.37	184	4.57	0.01	0.06
CC39868		34.8	2.29	2.54	0.09	0.34	0.05	0.027	0.09	12.3	25.6	1.33	262	7.37	0.02	0.05
CC39869		33.0	2.05	2.31	0.10	0.20	0.05	0.023	0.08	13.6	23.9	1.45	195	5.07	0.01	0.06
CC39870		36.9	2.02	2.34	0.09	0.20	0.06	0.025	0.09	12.9	21.9	1.47	215	5.86	0.02	0.07
CC39871		30.5	2.10	2.34	0.10	0.17	0.04	0.024	0.07	13.0	24.0	1.36	199	4.52	0.02	0.06
CC39872		41.8	1.95	2.42	0.12	0.20	0.11	0.025	0.09	15.7	18.9	1.50	192	10.20	0.02	0.09
CC39873		36.8	2.01	2.34	0.10	0.17	0.09	0.026	0.08	12.9	20.8	1.33	193	8.56	0.02	0.07
CC39874		37.6	2.01	2.05	0.10	0.19	0.07	0.024	0.06	12.0	20.0	1.24	186	8.85	0.02	0.06
CC39875		40.2	2.02	2.37	0.12	0.17	0.10	0.027	0.09	17.0	18.9	1.45	204	9.80	0.02	0.08
CC39876		67.2	4.06	2.30	0.12	0.19	0.10	0.031	0.09	13.3	17.7	1.31	229	14.90	0.02	0.09
CC39979		19.1	1.53	2.57	0.09	0.12	0.04	0.017	0.06	20.4	27.7	1.55	86	1.38	0.01	0.11
CC39980		22.5	1.79	2.77	0.09	0.12	0.05	0.020	0.06	21.1	27.7	1.27	158	2.05	0.01	0.13
CC39981		20.3	1.69	2.73	0.09	0.12	0.05	0.018	0.07	21.6	26.7	1.37	149	1.89	0.01	0.12
CC39982		17.2	1.76	2.28	0.09	0.14	0.02	0.018	0.06	18.3	24.6	2.82	376	2.80	0.01	0.08
CC39983		16.0	1.79	2.30	0.09	0.13	0.03	0.017	0.05	18.3	26.6	2.49	244	2.60	0.01	0.08
CC39984		14.9	1.59	2.39	0.10	0.11	0.03	0.015	0.06	21.0	25.9	1.58	130	1.82	0.01	0.09
CC39985		32.3	2.02	2.28	0.10	0.20	0.05	0.022	0.07	14.9	24.0	1.41	198	5.00	0.01	0.07
CC39986		33.2	2.00	2.46	0.10	0.19	0.05	0.023	0.09	12.7	24.9	1.59	207	5.18	0.01	0.07

Comments: Gold determinations by ME-MS41 are semi-quantitative due to the small sample weight used (0.5g).

ALS Chemex

EXCELLENCE IN ANALYTICAL CHEMISTRY

ALS Canada Ltd.

212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO

Finalized Date: 20-SEP-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07098783

Sample Description	Method	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41
	Analyte	Ni	P	Pb	Rb	Re	S	Sb	Sc	Se	Sn	Sr	Ta	Te	Th	Ti
	Units	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%
	LOR	0.2	10	0.2	0.1	0.001	0.01	0.05	0.1	0.2	0.2	0.2	0.01	0.01	0.2	0.005
CC39700		33.6	700	11.3	11.2	<0.001	0.05	1.86	3.6	3.4	0.4	51.5	<0.01	0.06	2.2	0.005
CC39701		22.0	450	10.0	10.4	<0.001	0.04	0.76	2.7	1.1	0.5	31.4	<0.01	0.05	2.8	0.008
CC39702		57.8	760	10.0	10.5	<0.001	0.07	1.69	3.5	2.3	0.5	87.9	<0.01	0.06	1.5	0.007
CC39703		55.0	540	10.7	9.2	<0.001	0.06	2.31	3.6	2.1	0.5	66.2	<0.01	0.06	2.8	0.007
CC39704		47.5	610	9.2	8.2	0.001	0.06	3.38	2.7	2.5	0.6	43.6	<0.01	0.07	1.6	0.007
CC39705		126.0	920	12.0	9.8	0.001	0.05	9.66	5.6	6.3	0.7	81.8	0.01	0.12	2.1	0.010
CC39706		138.5	790	12.0	9.2	0.001	0.09	12.40	3.8	11.0	0.5	90.8	0.01	0.11	1.3	0.009
CC39707		51.0	280	12.8	13.0	<0.001	0.03	2.76	4.4	1.8	0.6	11.2	0.01	0.06	5.8	0.020
CC39708		92.7	300	14.3	16.3	<0.001	0.02	3.91	5.2	2.3	0.7	13.3	0.01	0.09	5.9	0.018
CC39709		97.1	260	7.8	7.4	0.011	0.02	3.63	3.7	5.7	0.4	25.0	0.01	0.07	2.6	<0.005
CC39859		31.9	1070	18.6	7.1	0.009	0.18	2.47	3.2	2.1	0.3	223.0	<0.01	0.04	5.4	<0.005
CC39860		26.6	870	18.0	5.8	0.006	0.16	1.77	2.7	1.7	0.2	197.0	<0.01	0.03	5.1	<0.005
CC39861		33.5	870	20.7	6.4	0.007	0.18	2.27	3.1	1.8	0.2	217.0	<0.01	0.04	5.8	<0.005
CC39862		32.1	940	20.4	5.7	0.007	0.17	2.05	3.0	1.8	0.2	226.0	<0.01	0.04	5.7	<0.005
CC39863		26.0	880	17.3	5.2	0.006	0.16	1.73	2.7	1.6	0.2	198.0	<0.01	0.04	4.8	<0.005
CC39864		28.6	950	18.7	5.7	0.009	0.20	1.91	3.0	1.8	0.2	242.0	<0.01	0.04	5.4	<0.005
CC39865		25.2	790	16.9	4.8	0.005	0.15	1.47	2.5	1.4	0.2	182.0	<0.01	0.03	5.0	<0.005
CC39866		31.0	960	17.5	5.4	0.008	0.21	1.66	2.8	1.8	0.2	209.0	<0.01	0.04	5.2	<0.005
CC39867		27.6	900	17.0	5.5	0.008	0.20	1.65	2.8	1.7	0.2	202.0	<0.01	0.04	5.3	<0.005
CC39868		38.7	860	21.1	6.2	0.009	0.18	2.06	3.1	1.8	0.2	218.0	<0.01	0.04	6.1	<0.005
CC39869		28.1	950	17.7	5.9	0.008	0.19	1.77	2.9	1.9	0.2	214.0	<0.01	0.04	5.3	<0.005
CC39870		34.0	910	17.7	6.7	0.013	0.21	2.08	3.2	2.1	0.2	237.0	<0.01	0.05	5.2	<0.005
CC39871		30.7	870	18.4	5.7	0.006	0.16	1.73	2.8	1.6	0.2	204.0	<0.01	0.03	5.2	<0.005
CC39872		45.5	920	17.7	7.1	0.031	0.26	4.05	3.4	4.4	0.3	232.0	<0.01	0.05	5.2	<0.005
CC39873		40.8	860	16.7	6.4	0.023	0.21	3.14	3.1	2.8	0.2	202.0	<0.01	0.05	5.1	<0.005
CC39874		46.6	840	16.1	5.0	0.017	0.19	2.85	3.0	3.0	0.2	188.5	<0.01	0.04	4.9	<0.005
CC39875		53.1	930	16.4	6.8	0.026	0.23	3.51	3.4	3.3	0.3	231.0	<0.01	0.05	5.2	<0.005
CC39876		165.5	870	15.3	7.1	0.023	0.27	4.09	3.9	4.6	0.3	200.0	0.01	0.05	4.7	<0.005
CC39979		15.8	760	18.5	6.5	0.001	0.06	0.84	2.0	1.3	0.2	33.2	<0.01	0.02	5.1	<0.005
CC39980		19.6	770	19.7	7.7	0.002	0.06	1.06	2.3	1.6	0.2	41.9	<0.01	0.03	4.7	<0.005
CC39981		18.4	750	18.1	7.4	0.002	0.05	0.95	2.2	1.4	0.3	41.8	<0.01	0.02	4.9	<0.005
CC39982		18.8	750	22.9	5.5	0.001	0.02	1.13	1.8	1.1	0.2	73.3	<0.01	0.02	5.9	<0.005
CC39983		18.1	730	21.9	5.5	0.001	0.02	1.11	1.8	1.0	<0.2	53.1	<0.01	0.02	5.9	<0.005
CC39984		15.7	710	15.8	6.1	0.001	0.03	0.89	1.8	1.0	<0.2	34.8	<0.01	0.02	5.5	<0.005
CC39985		25.6	920	18.1	5.3	0.006	0.16	1.96	2.6	1.7	0.2	201.0	<0.01	0.04	5.3	<0.005
CC39986		25.1	1000	18.7	6.4	0.007	0.16	2.18	2.9	1.7	0.2	235.0	<0.01	0.04	5.1	<0.005

Comments: Gold determinations by ME-MS41 are semi-quantitative due to the small sample weight used (0.5g).

ALS Chemex

EXCELLENCE IN ANALYTICAL CHEMISTRY

ALS Canada Ltd.

212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: STRATEGIC METALS LTD.
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO

Finalized Date: 20-SEP-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07098783

Sample Description	Method	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41
	Analyte	Ti	U	V	W	Y	Zn	Zr
	Units	ppm	ppm	ppm	ppm	ppm	ppm	ppm
	LOR	0.02	0.05	1	0.05	0.05	2	0.5
CC39700		0.31	2.75	93	0.11	16.65	136	1.7
CC39701		0.13	0.74	44	0.08	5.85	89	1.4
CC39702		0.59	4.57	160	0.12	16.25	152	1.6
CC39703		0.44	4.09	258	0.14	14.25	183	1.6
CC39704		0.74	4.86	324	0.19	15.30	169	1.1
CC39705		1.20	4.96	408	0.20	32.80	1110	2.6
CC39706		0.82	5.36	496	0.23	33.40	1335	4.0
CC39707		0.37	1.07	144	0.18	4.42	245	4.5
CC39708		0.76	1.43	202	0.18	6.78	327	7.4
CC39709		1.23	3.68	107	0.14	25.10	299	1.2
CC39859		0.17	1.81	38	0.05	13.65	177	9.9
CC39860		0.13	1.33	25	<0.05	11.60	147	6.7
CC39861		0.14	1.63	35	0.05	12.40	169	14.4
CC39862		0.13	1.63	29	<0.05	12.50	167	11.8
CC39863		0.11	1.41	24	<0.05	11.45	137	7.1
CC39864		0.12	1.54	29	<0.05	12.45	150	12.1
CC39865		0.11	1.23	20	<0.05	10.50	131	7.3
CC39866		0.11	1.44	28	<0.05	12.50	162	9.6
CC39867		0.11	1.44	25	<0.05	12.20	159	8.3
CC39868		0.13	1.61	32	0.05	12.80	165	14.3
CC39869		0.11	1.50	29	<0.05	12.40	140	9.8
CC39870		0.14	1.74	34	<0.05	13.30	188	9.6
CC39871		0.13	1.38	25	<0.05	11.85	168	8.8
CC39872		0.29	3.26	128	0.07	15.05	344	10.1
CC39873		0.25	2.53	81	0.05	13.75	278	8.4
CC39874		0.32	2.26	56	0.05	13.80	298	8.9
CC39875		0.34	2.81	92	0.06	15.65	326	8.3
CC39876		0.53	6.69	109	0.09	28.40	1940	7.8
CC39979		0.10	0.80	18	<0.05	9.78	107	4.5
CC39980		0.11	1.02	21	<0.05	11.40	116	4.2
CC39981		0.11	0.88	20	<0.05	10.60	112	4.0
CC39982		0.08	0.89	19	<0.05	9.35	119	6.3
CC39983		0.07	0.83	17	<0.05	8.83	118	6.0
CC39984		0.08	0.78	16	<0.05	8.40	104	3.8
CC39985		0.12	1.46	27	<0.05	11.50	157	9.7
CC39986		0.14	1.67	34	<0.05	12.45	151	8.8

Comments: Gold determinations by ME-MS41 are semi-quantitative due to the small sample weight used (0.5g).

ALS Chemex
EXCELLENCE IN ANALYTICAL CHEMISTRY
ALS Canada Ltd.
212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Finalized Date: 25-SEP-2007
Account: MTT

CERTIFICATE VA07098782

Project: NIMO

P.O. No.:

This report is for 149 Soil samples submitted to our lab in Vancouver, BC, Canada on 15-AUG-2007.

The following have access to data associated with this certificate:

AL ARCHER VANCOUVER OFFICE	DOUG EATON BILL WENGZYNOWSKI	JOAN MARIACHER

SAMPLE PREPARATION

ALS CODE	DESCRIPTION
WEI-21	Received Sample Weight
LOG-22	Sample login - Rcd w/o BarCode
SCR-41	Screen to -180um and save both

ANALYTICAL PROCEDURES

ALS CODE	DESCRIPTION	INSTRUMENT
ME-OG46	Ore Grade Elements - AquaRegia	ICP-AES
Zn-OG46	Ore Grade Zn - Aqua Regia	VARIABLE
ME-MS41	51 anal. aqua regia ICPMS	

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

s is the Final Report and supersedes any preliminary report with this certificate number. Results apply to samples as submitted. All es of this report have been checked and approved for release.

Signature: Lawrence Ng

Lawrence Ng, Laboratory Manager - Vancouver

ALS Chemex

EXCELLENCE IN ANALYTICAL CHEMISTRY

ALS Canada Ltd.

212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO

Finalized Date: 25-SEP-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07098782

Sample Description	Method	WEI-21	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41
	Analyte	Recvd Wt.	Ag	Al	As	Au	B	Ba	Be	Bi	Ca	Cd	Ce	Co	Cr	Cs
	Units	kg	ppm	%	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppm	ppm	ppm
	LOR	0.02	0.01	0.01	0.1	0.2	10	10	0.05	0.01	0.01	0.01	0.02	0.1	1	0.05
CC27676		0.18	0.49	0.95	10.8	<0.2	10	400	0.74	0.17	5.35	1.76	42.70	16.3	17	2.16
CC27677		0.08	0.63	0.87	6.5	<0.2	10	350	0.66	0.16	5.06	3.01	34.90	8.3	15	1.71
CC27678		0.28	0.23	0.93	8.1	<0.2	<10	450	0.68	0.25	4.13	1.37	48.00	14.2	15	1.72
CC27679		0.12	1.41	0.48	9.7	<0.2	<10	1590	0.29	0.25	1.66	1.54	20.10	13.2	7	0.83
CC27680		0.18	0.93	0.56	6.0	<0.2	<10	2400	0.35	0.24	1.55	1.10	24.40	14.1	11	1.10
CC27681		0.22	0.92	0.46	9.0	<0.2	<10	2720	0.33	0.18	2.08	2.14	16.90	11.6	8	1.01
CC27682		0.24	0.73	0.57	16.6	<0.2	<10	2430	0.35	0.21	2.48	2.29	11.50	13.9	13	1.28
CC27750		0.16	0.24	0.69	8.4	<0.2	<10	300	0.45	0.15	5.51	0.96	33.70	8.1	11	0.78
CC27777		0.12	0.59	0.18	30.2	<0.2	<10	580	0.21	0.16	0.08	0.72	6.44	0.7	9	0.98
CC27778		0.16	0.37	0.21	14.9	<0.2	<10	350	0.17	0.13	0.07	0.39	7.67	0.8	9	1.24
CC27779		0.08	0.53	0.47	4.1	<0.2	<10	960	0.28	0.15	0.10	3.03	9.61	0.6	14	0.52
CC27780		0.14	0.60	1.23	17.3	<0.2	10	620	0.93	0.14	3.48	5.04	33.40	8.1	28	1.07
CC27781		0.12	0.58	1.00	15.1	<0.2	<10	600	0.78	0.11	3.84	9.96	27.40	7.0	26	0.92
CC27782		0.12	0.48	1.04	27.0	<0.2	<10	890	0.76	0.18	0.29	3.54	24.70	2.9	31	1.09
CC27783		0.10	0.50	1.06	27.6	<0.2	10	800	0.87	0.15	0.66	4.99	24.80	4.8	30	1.15
CC27784		0.18	0.60	1.18	20.0	<0.2	<10	770	1.09	0.16	0.78	7.69	29.50	6.7	32	0.92
CC27785		0.24	0.56	1.32	17.2	<0.2	<10	930	0.92	0.18	0.81	3.55	32.20	11.7	32	0.99
CC27786		0.32	0.45	1.37	10.8	<0.2	<10	950	0.80	0.18	0.40	2.60	33.10	9.2	31	0.82
CC27787		0.34	0.52	1.39	7.9	<0.2	10	980	0.90	0.17	0.71	3.07	37.10	8.2	30	0.88
CC27788		0.24	0.49	1.55	13.0	<0.2	10	790	1.00	0.18	1.75	2.69	37.80	8.9	29	0.91
CC27789		0.22	0.44	1.39	8.7	<0.2	10	650	0.76	0.16	2.18	2.30	34.40	7.7	26	0.95
CC27790		0.16	0.48	1.39	9.5	<0.2	<10	1340	0.87	0.17	1.71	2.86	31.40	10.4	28	0.61
CC27791		0.08	0.20	0.77	13.2	<0.2	<10	540	0.38	0.18	0.33	1.88	18.70	4.5	21	1.25
CC27792		0.20	0.64	1.45	15.9	<0.2	10	800	0.98	0.16	2.25	1.91	36.20	7.5	30	0.99
CC27793		0.46	0.26	0.71	21.0	<0.2	<10	280	0.31	0.20	0.03	0.69	15.95	5.2	14	0.71
CC27794		0.30	0.77	2.86	36.8	<0.2	<10	510	0.60	0.30	0.03	0.60	18.45	8.7	40	1.28
CC27795		0.40	0.61	0.40	22.6	<0.2	<10	450	0.38	0.14	0.01	0.86	9.92	1.0	13	0.41
CC27796		0.42	0.40	2.06	21.0	<0.2	<10	290	0.51	0.22	0.05	0.43	20.00	6.9	30	1.05
CC27797		0.12	0.30	1.18	3.5	<0.2	<10	490	0.57	0.20	0.80	0.47	32.10	9.2	16	0.86
CC27798		0.06	0.68	1.13	16.3	<0.2	10	530	0.76	0.10	2.31	2.83	27.30	15.7	19	1.21
CC27799		0.12	0.48	1.20	5.2	<0.2	10	710	0.68	0.08	1.80	1.57	29.10	5.0	21	1.18
CC27800		0.10	0.57	1.20	10.6	<0.2	10	690	0.75	0.13	2.56	2.00	32.60	10.0	21	1.14
CC27801		0.10	0.43	0.97	6.6	<0.2	<10	1320	0.50	0.16	1.12	1.55	25.10	6.0	17	0.65
CC27802		0.16	0.36	1.56	10.4	<0.2	<10	1060	0.74	0.21	0.93	0.75	30.40	14.2	26	0.68
CC27803		0.18	0.47	1.46	9.5	<0.2	10	740	0.93	0.18	1.65	1.55	29.80	8.8	26	0.63
CC27804		0.14	0.35	0.95	7.7	<0.2	10	900	0.60	0.08	1.60	1.65	22.00	25.5	18	0.77
CC27805		0.08	0.37	0.95	7.4	<0.2	10	980	0.63	0.09	1.61	1.66	22.80	10.4	19	0.78
CC27807		0.12	0.67	0.61	21.8	<0.2	10	2790	0.39	0.17	2.81	6.02	14.40	11.5	17	1.19
CC27808		0.22	0.67	0.59	19.6	<0.2	10	1180	0.48	0.16	3.09	5.90	17.40	10.5	17	1.15
CC27809		0.18	0.68	0.57	23.8	<0.2	10	1230	0.49	0.17	3.90	6.74	18.10	10.6	17	1.15

Comments: Gold determinations by ME-MS41 are semi-quantitative due to the small sample weight used (0.5g).

ALS Chemex
EXCELLENCE IN ANALYTICAL CHEMISTRY
ALS Canada Ltd.
212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: STRATEGIC METALS LTD.
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO

Finalized Date: 25-SEP-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07098782

Sample Description	Method	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41
	Analyte	Cu	Fe	Ga	Ge	Hf	Hg	In	K	La	Li	Mg	Mn	Mo	Na	Nb
	Units	ppm	%	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	%	ppm	ppm	%	ppm
	LOR	0.2	0.01	0.05	0.05	0.02	0.01	0.005	0.01	0.2	0.1	0.01	5	0.05	0.01	0.05
CC27676		47.4	2.37	3.21	0.09	0.12	0.12	0.027	0.16	22.4	14.4	1.52	263	4.56	0.02	0.24
CC27677		52.4	1.65	2.80	0.08	0.11	0.18	0.024	0.13	18.6	14.0	1.45	312	1.95	0.02	0.22
CC27678		29.2	2.66	2.85	0.07	0.23	0.10	0.032	0.14	22.2	13.0	0.88	423	3.95	0.01	0.07
CC27679		103.0	3.25	1.08	0.09	0.21	0.17	0.037	0.14	9.8	3.0	0.44	216	4.91	0.04	0.05
CC27680		69.3	2.57	1.40	0.07	0.18	0.12	0.031	0.12	12.1	4.9	0.52	260	2.39	0.05	0.05
CC27681		64.5	2.06	1.03	0.07	0.24	0.13	0.029	0.13	8.5	2.5	0.86	190	9.68	0.06	<0.05
CC27682		81.6	3.09	1.07	0.07	0.46	0.28	0.043	0.19	5.1	1.3	1.29	229	7.79	0.05	0.05
CC27750		26.1	1.88	1.98	0.06	0.14	0.06	0.018	0.06	16.6	22.3	2.98	230	2.77	0.02	0.08
CC27777		41.0	0.81	1.77	0.05	<0.02	0.07	0.021	0.08	3.6	0.5	0.02	7	34.20	0.01	0.07
CC27778		30.7	0.72	2.06	<0.05	<0.02	0.03	0.015	0.05	4.4	0.7	0.02	8	20.70	0.01	0.09
CC27779		63.8	0.44	1.62	0.07	0.04	0.18	0.029	0.03	4.7	1.1	0.02	8	37.50	0.02	0.19
CC27780		46.5	1.81	4.31	0.08	0.13	0.10	0.030	0.13	17.6	21.2	0.95	234	10.10	0.02	0.37
CC27781		47.2	1.37	3.58	0.07	0.11	0.09	0.028	0.10	14.8	17.3	0.94	217	6.33	0.02	0.32
CC27782		55.2	1.64	3.79	0.05	0.04	0.14	0.034	0.07	13.9	10.5	0.25	21	3.59	0.02	0.26
CC27783		46.8	1.87	3.83	0.07	0.07	0.14	0.030	0.08	14.0	15.0	0.44	21	3.73	0.02	0.27
CC27784		60.2	1.50	4.08	0.06	0.11	0.12	0.033	0.08	16.8	16.2	0.51	50	2.58	0.01	0.34
CC27785		38.8	1.67	4.37	0.06	0.12	0.12	0.036	0.09	16.0	19.3	0.60	182	5.60	0.02	0.49
CC27786		35.1	2.15	4.56	0.06	0.08	0.11	0.033	0.10	17.4	20.0	0.59	112	3.93	0.02	0.43
CC27787		43.8	1.88	4.65	0.06	0.13	0.09	0.033	0.12	19.9	21.7	0.73	98	3.74	0.02	0.38
CC27788		39.3	1.90	4.94	0.06	0.17	0.09	0.036	0.10	19.8	20.6	0.87	106	3.80	0.02	0.55
CC27789		39.9	1.56	4.53	0.05	0.12	0.08	0.033	0.10	18.2	19.9	0.98	127	1.84	0.02	0.53
CC27790		47.7	1.96	4.27	0.06	0.13	0.13	0.031	0.09	17.6	17.4	0.85	223	6.52	0.03	0.38
CC27791		19.8	1.58	4.51	<0.05	<0.02	0.07	0.022	0.07	8.7	6.3	0.15	201	15.05	0.02	0.40
CC27792		45.8	2.06	4.97	0.07	0.13	0.11	0.032	0.15	19.9	23.2	1.04	188	12.40	0.02	0.30
CC27793		29.5	2.24	3.41	0.05	0.02	0.05	0.024	0.08	8.0	3.3	0.07	105	26.50	<0.01	0.34
CC27794		36.4	4.34	7.36	0.06	0.15	0.06	0.056	0.10	9.2	28.8	0.31	189	23.30	0.01	0.89
CC27795		48.9	2.28	1.65	0.07	0.02	0.06	0.030	0.18	4.6	2.5	0.04	23	48.10	0.01	0.16
CC27796		22.7	3.16	5.58	0.05	0.17	0.07	0.037	0.07	10.1	23.6	0.33	144	14.95	0.01	0.70
CC27797		16.7	1.95	3.56	0.05	0.11	0.14	0.028	0.11	14.3	16.0	0.45	355	1.17	0.01	0.24
CC27798		39.6	2.99	3.59	0.08	0.14	0.18	0.018	0.13	14.8	23.8	0.97	1375	1.35	0.03	0.37
CC27799		29.6	1.52	3.81	0.07	0.13	0.11	0.015	0.17	15.5	23.0	1.00	281	0.59	0.03	0.37
CC27800		39.2	2.43	3.87	0.07	0.12	0.12	0.023	0.15	17.0	20.9	1.03	475	2.92	0.02	0.41
CC27801		29.5	1.69	3.10	0.05	0.06	0.11	0.023	0.08	12.6	11.7	0.37	222	1.44	0.03	0.40
CC27802		28.6	2.60	4.88	0.05	0.07	0.08	0.033	0.09	15.5	17.2	0.46	462	4.00	0.03	0.46
CC27803		51.5	2.22	4.39	0.08	0.16	0.09	0.030	0.10	16.2	17.1	0.68	219	2.28	0.01	0.68
CC27804		23.2	4.84	3.09	0.10	0.09	0.12	0.013	0.10	12.1	12.9	0.58	1060	1.57	0.01	0.37
CC27805		26.5	3.80	3.01	0.11	0.09	0.15	0.014	0.11	12.5	12.5	0.57	416	1.53	0.01	0.33
CC27807		71.4	2.72	1.66	0.10	0.28	0.32	0.034	0.19	7.1	1.9	1.23	202	25.90	0.02	0.09
CC27808		64.0	2.60	1.75	0.10	0.16	0.30	0.027	0.16	9.1	3.0	1.25	200	26.20	0.01	0.11
CC27809		66.8	2.58	1.66	0.12	0.25	0.27	0.031	0.16	9.3	2.8	1.22	205	31.00	0.01	0.08

Comments: Gold determinations by ME-MS41 are semi-quantitative due to the small sample weight used (0.5g).

ALS Chemex

EXCELLENCE IN ANALYTICAL CHEMISTRY

ALS Canada Ltd.

212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO

Finalized Date: 25-SEP-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07098782

Sample Description	Method	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41
	Analyte	Ni	P	Pb	Rb	Re	S	Sb	Sc	Se	Sn	Sr	Ta	Te	Th	Ti
	Units	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%
	LOR	0.2	10	0.2	0.1	0.001	0.01	0.05	0.1	0.2	0.2	0.2	0.01	0.01	0.2	0.005
CC27676		44.8	2930	17.5	13.6	0.003	0.12	2.79	3.3	2.3	0.4	109.0	<0.01	0.07	3.9	0.007
CC27677		42.6	2030	13.5	13.0	0.005	0.22	1.93	3.0	3.5	0.4	95.3	<0.01	0.03	2.6	0.007
CC27678		38.4	1100	16.4	11.0	0.006	0.21	1.41	4.0	1.5	0.3	116.5	<0.01	0.05	6.3	<0.005
CC27679		72.4	810	14.5	6.4	0.007	0.25	2.57	5.3	10.9	0.2	75.5	<0.01	0.06	4.9	<0.005
CC27680		51.4	800	12.2	7.1	0.007	0.21	1.52	5.3	3.5	0.2	83.0	<0.01	0.05	5.3	<0.005
CC27681		59.9	760	10.6	7.0	0.016	0.19	3.16	4.7	4.1	0.2	122.0	<0.01	0.05	4.1	<0.005
CC27682		85.5	580	9.7	10.1	0.009	0.25	3.43	7.7	4.4	0.3	165.0	<0.01	0.04	4.8	<0.005
CC27750		25.6	850	31.7	5.4	0.001	0.04	1.20	2.2	1.5	0.2	79.1	<0.01	0.01	5.0	<0.005
CC27777		14.4	330	10.8	9.1	0.023	0.16	8.07	1.2	5.1	0.6	31.7	<0.01	0.18	0.9	<0.005
CC27778		12.6	300	7.4	8.7	0.019	0.07	5.48	1.0	5.1	0.6	16.3	<0.01	0.13	1.0	<0.005
CC27779		18.6	820	6.4	3.7	0.045	0.28	7.04	1.7	12.2	0.4	14.0	<0.01	0.06	0.3	0.008
CC27780		66.0	1630	10.4	14.1	0.002	0.06	5.23	4.3	3.6	0.5	140.0	<0.01	0.05	2.5	0.010
CC27781		77.6	1270	8.6	11.5	0.002	0.06	6.11	3.9	3.0	0.4	159.5	<0.01	0.04	2.2	0.010
CC27782		70.2	490	12.0	11.8	0.009	0.04	8.50	4.1	5.7	0.6	31.3	<0.01	0.09	3.1	0.006
CC27783		77.3	840	11.0	12.6	0.008	0.05	6.52	4.0	5.0	0.6	51.0	<0.01	0.08	3.6	0.007
CC27784		107.5	840	12.0	11.7	0.004	0.04	6.62	5.3	4.5	0.6	55.3	<0.01	0.06	4.4	0.007
CC27785		75.0	1040	13.1	12.9	0.005	0.06	5.01	5.5	4.2	0.6	55.5	<0.01	0.04	5.2	0.014
CC27786		56.5	1030	11.4	13.7	0.003	0.03	3.80	4.9	3.5	0.5	37.5	<0.01	0.05	5.1	0.012
CC27787		64.8	1200	11.6	15.1	0.001	0.01	3.67	5.5	1.6	0.5	47.4	<0.01	0.04	5.7	0.016
CC27788		57.5	1130	13.1	13.6	0.002	0.04	2.81	5.9	2.0	0.6	77.4	<0.01	0.05	5.7	0.015
CC27789		52.7	1120	12.0	12.8	0.002	0.06	2.81	5.3	2.0	0.6	93.4	<0.01	0.04	5.0	0.015
CC27790		131.5	970	9.7	10.4	0.001	0.04	3.50	5.3	1.9	0.5	94.1	<0.01	0.04	3.6	0.013
CC27791		30.8	660	11.2	10.8	0.003	0.05	3.61	2.0	2.3	0.6	24.8	<0.01	0.06	1.0	0.013
CC27792		75.0	1760	10.4	15.2	0.001	0.03	4.09	5.5	2.0	0.6	108.0	<0.01	0.04	4.0	0.012
CC27793		70.5	330	10.6	12.5	0.001	0.04	3.97	2.2	3.5	0.6	27.0	<0.01	0.04	2.4	0.008
CC27794		52.6	450	17.9	18.2	<0.001	0.06	4.87	4.5	4.7	0.9	33.7	<0.01	0.14	5.3	0.014
CC27795		11.8	520	9.6	10.9	0.003	0.54	14.05	1.9	9.2	0.5	127.5	<0.01	0.13	1.5	0.006
CC27796		30.1	250	12.8	14.0	<0.001	0.02	5.78	3.3	2.0	0.7	17.1	<0.01	0.06	4.7	0.019
CC27797		23.3	720	11.0	15.2	<0.001	0.07	0.52	3.8	1.1	0.4	35.0	<0.01	0.03	3.6	0.006
CC27798		33.2	2040	8.1	16.0	0.005	0.16	1.51	3.0	5.2	0.4	96.9	<0.01	0.07	1.8	0.010
CC27799		25.5	2350	7.0	16.2	0.003	0.10	0.99	3.0	2.3	0.4	70.7	<0.01	0.01	2.7	0.012
CC27800		33.6	2030	9.7	15.0	0.003	0.10	2.12	3.5	3.4	0.4	96.6	<0.01	0.05	3.0	0.013
CC27801		26.5	860	9.7	10.4	0.005	0.09	1.06	3.3	3.2	0.4	55.3	<0.01	0.02	2.8	0.011
CC27802		36.0	790	12.3	11.4	0.001	0.02	1.46	4.7	1.5	0.6	45.7	<0.01	0.04	3.6	0.012
CC27803		42.4	980	12.1	10.5	<0.001	0.05	1.91	5.1	1.9	0.5	68.8	<0.01	0.06	4.0	0.016
CC27804		61.9	1390	6.6	11.8	0.003	0.09	1.11	2.9	2.7	0.3	74.3	<0.01	0.03	2.6	0.011
CC27805		39.4	1640	7.2	12.6	0.003	0.10	1.22	2.9	3.2	0.4	73.5	<0.01	0.03	2.6	0.010
CC27807		99.5	770	10.1	11.5	0.015	0.17	8.95	6.3	5.6	0.5	184.5	<0.01	0.07	4.3	<0.005
CC27808		89.7	870	10.4	10.3	0.021	0.27	7.63	5.2	5.3	0.4	181.5	<0.01	0.08	3.7	<0.005
CC27809		100.5	790	10.6	10.0	0.031	0.25	8.47	5.7	6.4	0.5	213.0	<0.01	0.10	4.3	<0.005

Comments: Gold determinations by ME-MS41 are semi-quantitative due to the small sample weight used (0.5g).

ALS Chemex

EXCELLENCE IN ANALYTICAL CHEMISTRY

ALS Canada Ltd.

212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: STRATEGIC METALS LTD.
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Finalized Date: 25-SEP-2007
Account: MTT

Project: NIMO

CERTIFICATE OF ANALYSIS VA07098782

Sample Description	Method	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	Zn-OG46
	Analyte	Tl	U	V	W	Y	Zn	Zr	Zn
	Units	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%
	LOR	0.02	0.05	1	0.05	0.05	2	0.5	0.01
CC27676		0.16	2.44	86	0.06	18.50	244	4.0	
CC27677		0.20	2.23	62	0.05	16.20	244	3.2	
CC27678		0.10	1.39	31	<0.05	14.50	184	8.3	
CC27679		0.12	3.24	20	<0.05	14.05	293	8.3	
CC27680		0.10	2.01	22	<0.05	13.15	216	7.3	
CC27681		0.13	3.45	41	<0.05	13.90	296	8.9	
CC27682		0.14	2.93	33	<0.05	17.55	282	14.2	
CC27750		0.08	0.98	18	<0.05	10.05	163	5.5	
CC27777		1.97	5.37	105	0.28	3.96	61	<0.5	
CC27778		1.29	2.56	106	0.18	4.17	39	<0.5	
CC27779		0.64	5.05	90	0.09	7.94	18	1.1	
CC27780		0.69	1.91	193	0.12	19.35	481	3.4	
CC27781		0.71	1.55	239	0.12	17.30	1100	3.3	
CC27782		1.49	3.98	349	0.16	18.50	406	1.2	
CC27783		1.37	2.51	374	0.17	18.05	600	2.6	
CC27784		1.10	2.86	332	0.15	22.30	718	4.3	
CC27785		0.82	3.98	254	0.11	17.35	499	4.6	
CC27786		0.58	2.27	222	0.12	16.00	373	2.9	
CC27787		0.55	1.30	196	0.12	18.75	394	5.6	
CC27788		0.61	1.28	145	0.13	18.85	282	5.9	
CC27789		0.65	1.14	118	0.09	17.40	306	4.2	
CC27790		0.55	1.85	133	0.13	33.20	459	3.6	
CC27791		0.69	1.66	192	0.16	4.94	168	<0.5	
CC27792		0.55	1.54	187	0.12	22.20	333	3.2	
CC27793		1.29	1.88	153	0.13	4.09	240	0.6	
CC27794		1.35	1.65	235	0.17	3.74	151	4.6	
CC27795		2.56	9.17	161	0.17	6.14	43	1.2	
CC27796		0.65	1.06	172	0.15	2.70	105	4.9	
CC27797		0.13	1.13	27	0.05	10.25	87	2.5	
CC27798		0.19	1.80	88	0.07	13.80	214	3.1	
CC27799		0.20	2.01	100	0.07	13.25	180	3.2	
CC27800		0.19	1.91	97	0.17	14.95	203	3.0	
CC27801		0.17	1.49	56	0.09	10.30	134	1.5	
CC27802		0.19	1.26	82	0.11	12.10	146	1.7	
CC27803		0.17	1.27	79	0.12	13.95	149	5.1	
CC27804		0.25	1.61	95	0.06	10.05	318	2.4	
CC27805		0.26	1.90	108	0.05	10.95	255	2.5	
CC27807		0.24	5.18	146	0.07	19.50	656	11.8	
CC27808		0.35	5.42	153	0.09	18.95	562	7.8	
CC27809		0.44	5.94	155	0.08	20.10	605	11.4	

Comments: Gold determinations by ME-MS41 are semi-quantitative due to the small sample weight used (0.5g).

ALS Chemex

EXCELLENCE IN ANALYTICAL CHEMISTRY

ALS Canada Ltd.

212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: STRATEGIC METALS LTD.
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO

Finalized Date: 25-SEP-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07098782

Sample Description	Method	WEI-21	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41
	Analyte	Recvd Wt.	Ag	Al	As	Au	B	Ba	Be	Bi	Ca	Cd	Ce	Co	Cr	Cs
	Units	kg	ppm	%	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppm	ppm	ppm
	LOR	0.02	0.01	0.01	0.1	0.2	10	10	0.05	0.01	0.01	0.01	0.02	0.1	1	0.05
CC27810		0.26	1.11	0.64	40.8	<0.2	<10	1020	0.71	0.19	2.93	30.00	19.70	14.4	19	1.17
CC27811		0.10	0.48	0.42	26.3	<0.2	<10	890	0.46	0.18	0.99	15.85	10.95	5.2	14	0.65
CC27812		0.20	0.78	0.55	33.8	<0.2	<10	1580	0.53	0.22	2.21	10.75	18.45	18.0	18	0.99
CC27813		0.14	0.60	0.80	5.6	<0.2	<10	400	0.61	0.09	2.25	2.90	24.00	4.2	16	0.79
CC27814		0.06	0.77	0.83	6.9	<0.2	<10	430	0.61	0.12	2.36	3.34	26.20	5.6	17	0.81
CC27815		0.12	0.64	1.03	7.1	<0.2	<10	460	0.72	0.13	1.58	2.62	33.30	6.5	18	0.83
CC27816		0.22	0.36	1.02	4.1	<0.2	<10	650	0.49	0.10	0.88	1.03	34.20	6.0	17	0.79
CC27817		0.18	0.74	0.99	5.2	<0.2	<10	660	0.54	0.16	1.78	2.21	31.30	6.6	17	0.70
CC27818		0.12	0.69	0.89	8.1	<0.2	<10	1770	0.63	0.16	1.70	6.25	28.50	7.0	17	0.72
CC27819		0.06	0.85	0.85	10.3	<0.2	<10	1450	0.68	0.17	2.04	7.94	27.90	7.3	17	0.62
CC27820		0.20	0.69	0.96	21.5	<0.2	10	1810	0.95	0.12	3.22	11.10	26.70	12.9	28	0.90
CC27821		0.18	0.95	0.56	41.5	<0.2	<10	1090	0.77	0.16	3.29	15.25	20.10	13.8	26	0.90
CC27822		0.24	0.80	0.64	28.4	<0.2	10	1770	0.72	0.15	3.19	6.35	21.70	10.7	26	1.09
CC27823		0.22	0.85	0.79	29.2	<0.2	<10	4100	0.80	0.17	0.28	4.87	22.80	1.5	49	0.88
CC27824		0.12	0.55	1.22	14.2	<0.2	10	3590	0.89	0.24	0.59	2.98	43.20	9.6	30	1.03
CC27825		0.24	0.91	1.00	11.4	<0.2	10	3390	0.65	0.22	1.06	1.30	35.30	11.4	22	0.85
CC27826		0.20	0.83	1.16	10.0	<0.2	<10	2730	0.79	0.24	0.77	0.66	36.10	5.0	24	0.91
CC27827		0.22	2.86	2.00	47.3	<0.2	10	3850	1.16	0.27	0.18	25.90	27.60	8.6	85	1.66
CC27828		0.30	0.31	0.75	26.4	<0.2	10	610	0.82	0.16	0.51	3.37	23.80	7.7	16	0.69
CC27829		0.18	0.38	1.46	14.4	<0.2	10	1300	1.05	0.15	0.43	1.56	30.80	8.2	29	1.11
CC27830		0.40	0.41	0.56	22.7	<0.2	<10	510	0.44	0.19	0.46	0.88	16.15	2.2	14	0.72
CC27831		0.18	0.56	1.44	13.8	<0.2	10	1000	1.00	0.13	3.22	2.72	31.60	8.7	28	0.73
CC27832		0.30	0.44	1.32	9.5	<0.2	<10	1100	0.89	0.14	1.98	2.42	29.10	8.1	24	0.59
CC27833		0.40	0.38	1.38	5.6	<0.2	10	1080	0.99	0.14	1.99	2.39	34.00	6.4	26	0.69
CC27834		0.12	0.27	0.48	25.7	<0.2	<10	130	0.20	0.13	0.06	1.42	9.24	1.9	21	0.89
CC27835		0.10	0.60	0.46	26.1	<0.2	<10	360	0.40	0.14	0.55	4.92	9.46	4.8	17	0.64
CC27836		0.30	0.38	0.59	28.1	<0.2	<10	350	0.59	0.18	0.38	3.16	14.45	7.3	16	0.66
CC27837		0.34	0.24	0.29	4.1	<0.2	<10	110	0.12	0.12	0.02	0.50	8.09	0.7	8	0.77
CC27838		0.30	2.43	1.10	24.4	<0.2	<10	1640	1.41	0.16	0.95	26.90	12.75	4.3	32	0.49
CC27839		0.22	1.07	0.90	16.4	<0.2	<10	190	0.26	0.25	0.03	0.82	12.60	2.1	23	0.82
CC27840		0.22	0.54	0.46	12.1	<0.2	<10	180	0.36	0.15	0.02	0.33	8.44	1.1	13	0.47
CC27841		0.16	1.04	0.58	5.3	<0.2	<10	290	0.21	0.14	0.04	0.94	14.45	1.0	12	0.94
CC27842		0.22	0.54	0.89	9.0	<0.2	10	1550	0.44	0.36	0.04	3.03	15.80	1.7	19	1.52
CC27843		0.24	1.36	0.81	20.5	<0.2	<10	700	0.33	0.43	0.05	1.22	12.45	0.9	26	1.17
CC27844		0.16	2.45	0.55	18.6	<0.2	<10	620	0.24	0.26	0.06	1.54	9.85	0.9	14	0.61
CC27845		0.16	1.55	0.35	9.9	<0.2	<10	290	0.13	0.22	0.06	1.19	7.32	0.6	14	0.71
CC27846		0.32	0.20	0.45	17.5	<0.2	<10	860	0.51	0.15	0.11	1.17	14.65	6.4	8	0.42
CC27847		0.24	0.84	0.40	27.3	<0.2	<10	360	0.42	0.15	0.70	1.84	10.80	6.6	11	0.46
CC27848		0.14	0.34	0.55	43.3	<0.2	<10	210	0.33	0.16	0.25	2.06	11.40	6.5	19	0.67
CC27849		0.20	1.07	1.15	21.0	<0.2	<10	1800	0.52	0.17	1.27	7.51	34.10	14.6	26	0.86

Comments: Gold determinations by ME-MS41 are semi-quantitative due to the small sample weight used (0.5g).

ALS Chemex

EXCELLENCE IN ANALYTICAL CHEMISTRY

ALS Canada Ltd.

212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO

Finalized Date: 25-SEP-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07098782

Sample Description	Method	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41
	Analyte	Cu	Fe	Ga	Ge	Hf	Hg	In	K	La	Li	Mg	Mn	Mo	Na	Nb
	Units	ppm	%	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	%	ppm	ppm	%	ppm
	LOR	0.2	0.01	0.05	0.05	0.02	0.01	0.005	0.01	0.2	0.1	0.01	5	0.05	0.01	0.05
CC27810		104.0	5.52	1.81	0.21	0.23	0.33	0.046	0.16	10.3	2.6	0.95	213	50.90	0.01	0.11
CC27811		63.7	5.01	1.67	0.12	0.04	0.22	0.029	0.11	5.4	0.9	0.17	70	34.90	<0.01	0.09
CC27812		78.4	3.51	1.80	0.09	0.18	0.29	0.043	0.15	9.7	2.9	0.84	268	35.20	0.01	0.10
CC27813		45.8	1.11	2.54	0.07	0.09	0.17	0.015	0.07	14.8	8.6	0.53	148	0.72	0.01	0.36
CC27814		53.0	1.34	2.61	0.09	0.11	0.21	0.018	0.07	16.2	8.5	0.47	276	0.85	0.01	0.40
CC27815		43.8	1.59	3.24	0.09	0.12	0.18	0.019	0.10	18.8	10.8	0.44	276	1.36	0.01	0.35
CC27816		24.1	1.57	3.35	0.08	0.08	0.10	0.015	0.10	18.0	10.5	0.39	213	0.77	<0.01	0.24
CC27817		48.2	1.50	2.74	0.07	0.12	0.20	0.024	0.07	17.0	8.5	0.36	395	0.91	0.01	0.35
CC27818		49.2	1.60	2.67	0.08	0.10	0.20	0.025	0.08	15.3	7.8	0.38	367	5.36	0.01	0.32
CC27819		68.4	1.70	2.45	0.10	0.11	0.25	0.025	0.07	15.1	6.9	0.37	437	6.27	0.01	0.31
CC27820		62.2	1.90	3.52	0.13	0.10	0.14	0.028	0.15	14.8	11.8	1.68	177	15.40	0.01	0.26
CC27821		83.4	2.33	2.37	0.14	0.13	0.23	0.034	0.11	10.8	3.6	0.95	246	40.40	0.01	0.15
CC27822		72.8	2.10	2.70	0.13	0.21	0.21	0.029	0.14	11.5	4.6	1.38	235	32.50	0.01	0.14
CC27823		43.8	1.17	4.54	0.07	0.03	0.24	0.020	0.07	14.2	9.3	0.18	35	15.25	0.01	0.77
CC27824		54.4	2.35	4.01	0.12	0.08	0.18	0.040	0.13	24.1	10.3	0.27	194	9.17	0.01	0.31
CC27825		44.7	3.38	3.01	0.12	0.08	0.17	0.038	0.12	19.8	7.2	0.31	325	10.55	0.01	0.24
CC27826		37.2	2.78	3.46	0.10	0.08	0.14	0.038	0.11	20.2	7.8	0.23	109	2.93	0.01	0.25
CC27827		191.0	2.43	6.45	0.11	0.07	1.03	0.042	0.14	16.2	12.1	0.30	255	28.90	0.01	0.71
CC27828		43.2	1.96	2.24	0.07	0.07	0.09	0.025	0.10	14.1	3.7	0.16	70	21.40	<0.01	0.11
CC27829		44.2	2.63	4.28	0.09	0.07	0.15	0.036	0.11	16.6	12.6	0.53	185	13.95	<0.01	0.33
CC27830		14.6	1.89	2.10	0.07	0.03	0.07	0.016	0.11	7.9	3.6	0.10	42	24.30	<0.01	0.22
CC27831		44.1	1.92	4.47	0.10	0.12	0.11	0.029	0.09	19.2	15.4	1.26	329	7.91	0.01	0.41
CC27832		31.2	1.91	4.13	0.08	0.09	0.09	0.027	0.07	16.7	11.1	0.42	276	2.45	0.01	0.44
CC27833		29.8	1.54	4.29	0.08	0.10	0.09	0.027	0.10	19.2	14.8	0.66	169	0.78	0.01	0.40
CC27834		20.9	1.15	3.55	0.06	<0.02	0.04	0.015	0.04	5.4	0.6	0.03	22	45.10	<0.01	0.23
CC27835		31.2	1.18	1.96	0.06	0.04	0.12	0.019	0.05	5.5	1.3	0.05	49	35.10	0.01	0.26
CC27836		47.2	2.16	2.31	0.09	0.02	0.09	0.027	0.07	8.1	3.1	0.09	101	47.40	<0.01	0.19
CC27837		9.7	0.41	2.76	<0.05	<0.02	0.02	0.006	0.04	4.5	0.4	0.02	16	7.97	<0.01	0.17
CC27838		85.2	1.59	2.87	0.10	0.14	0.25	0.035	0.10	6.8	2.2	0.13	288	17.95	<0.01	0.14
CC27839		20.1	2.03	5.36	0.06	<0.02	0.04	0.027	0.06	6.8	4.0	0.09	80	16.10	<0.01	0.68
CC27840		56.7	0.67	1.81	<0.05	<0.02	0.03	0.018	0.06	4.5	1.7	0.04	24	10.50	0.01	0.20
CC27841		15.8	0.63	3.20	<0.05	<0.02	0.05	0.016	0.04	7.4	1.0	0.03	16	4.30	0.01	0.24
CC27842		90.7	1.19	5.15	0.08	<0.02	0.22	0.045	0.08	8.5	0.8	0.02	12	12.65	0.01	0.24
CC27843		44.0	1.45	5.83	0.07	<0.02	0.25	0.040	0.14	8.3	1.3	0.04	17	38.30	0.01	0.37
CC27844		31.5	1.57	3.03	0.08	<0.02	0.06	0.043	0.19	6.8	1.0	0.03	13	37.10	0.01	0.24
CC27845		14.6	0.81	2.79	<0.05	<0.02	0.03	0.023	0.12	4.8	0.6	0.02	20	18.45	0.01	0.18
CC27846		35.0	1.88	1.49	0.06	0.02	0.06	0.026	0.08	9.4	1.2	0.03	49	32.50	0.01	0.12
CC27847		39.4	1.64	1.27	<0.05	0.03	0.11	0.027	0.05	7.5	1.2	0.03	53	35.80	0.01	0.14
CC27848		41.3	1.94	2.73	0.05	<0.02	0.05	0.029	0.06	7.7	1.8	0.05	52	46.40	0.01	0.30
CC27849		49.1	1.52	3.15	0.07	0.07	0.24	0.032	0.08	14.4	8.4	0.18	232	24.80	0.02	0.36

Comments: Gold determinations by ME-MS41 are semi-quantitative due to the small sample weight used (0.5g).

ALS Chemex

EXCELLENCE IN ANALYTICAL CHEMISTRY

ALS Canada Ltd.

212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: STRATEGIC METALS LTD.
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO

Finalized Date: 25-SEP-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07098782

Sample Description	Method	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41
	Analyte	Ni	P	Pb	Rb	Re	S	Sb	Sc	Se	Sn	Sr	Ta	Te	Th	Ti
	Units	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%
	LOR	0.2	10	0.2	0.1	0.001	0.01	0.05	0.1	0.2	0.2	0.2	0.01	0.01	0.2	0.005
CC27810		157.5	1080	13.0	10.8	0.031	0.36	13.40	6.2	12.3	0.6	184.5	0.01	0.16	4.4	<0.005
CC27811		86.7	410	11.1	7.9	0.029	0.33	3.15	3.2	8.0	0.5	81.9	<0.01	0.16	1.6	<0.005
CC27812		125.0	780	12.1	9.4	0.031	0.26	7.75	5.4	8.3	0.5	141.5	<0.01	0.14	4.0	<0.005
CC27813		31.9	1780	8.6	7.9	0.006	0.12	1.66	2.6	3.4	0.3	43.5	<0.01	0.04	1.4	0.012
CC27814		38.4	1550	10.5	8.4	0.009	0.15	2.00	3.1	4.1	0.4	51.2	0.01	0.05	1.6	0.012
CC27815		33.7	1580	11.3	10.9	0.006	0.10	1.65	3.1	3.6	0.5	41.7	<0.01	0.05	2.0	0.008
CC27816		24.9	1250	8.6	11.1	0.004	0.06	0.76	2.8	1.6	0.4	31.4	<0.01	0.02	3.3	0.007
CC27817		32.3	1130	11.4	8.8	0.010	0.16	1.32	3.5	3.7	0.5	46.9	<0.01	0.05	1.9	0.009
CC27818		75.8	1060	12.1	9.7	0.009	0.15	2.15	3.6	4.2	0.6	87.4	<0.01	0.05	1.9	0.008
CC27819		89.0	1100	12.4	9.3	0.013	0.20	2.50	3.8	5.4	0.6	95.5	<0.01	0.06	1.7	0.008
CC27820		102.5	2290	10.3	13.7	0.015	0.11	5.48	3.9	5.6	0.5	196.5	<0.01	0.07	2.6	0.008
CC27821		165.5	1080	12.0	9.6	0.050	0.28	10.90	5.0	11.5	0.6	209.0	<0.01	0.14	3.2	<0.005
CC27822		110.5	1660	11.3	11.5	0.045	0.24	9.16	5.3	8.0	0.6	269.0	<0.01	0.10	4.0	0.005
CC27823		31.9	690	10.2	13.7	0.009	0.09	5.92	2.2	4.3	0.8	73.5	<0.01	0.11	0.9	0.016
CC27824		75.5	870	15.4	16.9	0.011	0.08	3.11	6.4	5.7	0.6	82.7	<0.01	0.08	5.4	0.005
CC27825		66.5	780	13.3	12.8	0.004	0.06	2.43	6.4	5.3	0.5	88.1	<0.01	0.06	4.4	0.005
CC27826		29.3	720	16.2	14.2	0.006	0.07	1.58	5.6	5.5	0.4	79.7	<0.01	0.07	4.2	<0.005
CC27827		115.0	1530	14.7	20.6	0.002	0.10	18.30	6.0	5.8	1.0	66.1	<0.01	0.18	1.5	0.019
CC27828		126.5	350	10.9	9.0	0.002	0.02	7.19	4.6	3.4	0.6	44.5	<0.01	0.10	4.3	<0.005
CC27829		71.8	730	11.1	13.4	<0.001	0.03	4.76	4.9	2.5	0.7	32.8	<0.01	0.07	3.6	0.007
CC27830		29.2	310	14.1	9.9	<0.001	0.14	10.30	2.1	4.1	0.6	50.1	<0.01	0.08	3.7	0.006
CC27831		76.2	1230	9.5	11.8	<0.001	0.05	2.55	4.2	2.1	0.6	169.0	<0.01	0.06	1.8	0.010
CC27832		42.2	780	9.6	10.5	<0.001	0.06	1.65	3.7	2.0	0.5	90.7	<0.01	0.05	1.6	0.007
CC27833		44.7	1190	10.0	12.3	<0.001	0.06	1.35	4.3	1.8	0.5	84.3	<0.01	0.05	2.8	0.007
CC27834		133.5	260	7.4	5.8	0.001	0.01	7.33	1.3	4.8	0.8	6.5	<0.01	0.12	0.6	0.011
CC27835		112.0	770	9.6	6.6	0.004	0.10	7.39	2.4	5.5	0.7	39.2	<0.01	0.09	0.7	0.006
CC27836		169.0	360	10.6	9.1	0.005	0.03	6.45	3.4	5.8	0.6	41.7	<0.01	0.09	1.4	0.006
CC27837		6.7	150	6.5	6.4	<0.001	0.01	2.62	0.9	1.5	0.7	11.0	<0.01	0.07	0.7	0.008
CC27838		134.5	2180	12.7	9.0	0.002	0.11	26.50	3.7	9.7	0.8	277.0	<0.01	0.24	1.1	<0.005
CC27839		11.7	270	14.0	11.5	<0.001	0.04	12.05	2.0	4.5	0.8	25.1	<0.01	0.20	1.9	0.019
CC27840		13.3	240	9.9	6.9	0.005	0.09	4.19	2.3	3.9	0.4	16.1	<0.01	0.11	1.4	0.005
CC27841		12.0	400	8.4	5.6	0.001	0.04	1.73	0.6	2.4	0.7	10.8	<0.01	0.07	<0.2	0.009
CC27842		42.3	510	23.2	8.7	0.010	0.08	2.97	1.1	12.6	1.2	29.0	<0.01	0.19	<0.2	<0.005
CC27843		8.7	620	25.6	14.9	0.003	0.24	8.97	1.3	9.7	1.5	63.1	<0.01	0.27	0.7	0.005
CC27844		8.2	830	18.9	12.1	0.002	0.41	14.60	1.3	14.8	1.0	85.4	<0.01	0.20	0.7	0.005
CC27845		5.5	440	16.2	9.0	0.001	0.20	8.02	0.7	5.9	0.8	35.8	<0.01	0.13	0.4	0.005
CC27846		94.7	200	9.5	7.5	0.006	0.07	2.22	3.1	4.9	0.4	32.9	<0.01	0.08	1.9	<0.005
CC27847		141.5	360	9.4	6.2	0.005	0.05	5.92	2.8	4.2	0.6	41.8	<0.01	0.11	1.1	<0.005
CC27848		191.0	320	10.0	8.3	0.007	0.04	7.57	2.2	6.0	0.7	17.0	<0.01	0.14	0.8	0.006
CC27849		82.2	650	9.6	10.9	0.032	0.19	6.84	3.6	6.6	0.5	78.1	<0.01	0.06	1.8	0.005

Comments: Gold determinations by ME-MS41 are semi-quantitative due to the small sample weight used (0.5g).

ALS Chemex

EXCELLENCE IN ANALYTICAL CHEMISTRY

ALS Canada Ltd.

212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: STRATEGIC METALS LTD.
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO

Finalized Date: 25-SEP-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07098782

Sample Description	Method	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	Zn-OG46
	Analyte	Tl	U	V	W	Y	Zn	Zr	Zn
	Units	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%
	LOR	0.02	0.05	1	0.05	0.05	2	0.5	0.01
CC27810		1.75	6.83	167	0.16	30.80	1530	10.7	
CC27811		2.20	4.48	79	0.25	24.30	1020	1.9	
CC27812		0.92	5.47	137	0.14	22.30	849	7.8	
CC27813		0.20	2.83	77	0.05	15.35	298	2.7	
CC27814		0.21	2.70	70	0.06	16.50	306	3.1	
CC27815		0.17	3.05	68	0.06	16.50	261	2.8	
CC27816		0.14	1.86	45	0.29	11.70	168	2.1	
CC27817		0.16	2.39	48	0.05	17.75	190	3.2	
CC27818		0.68	2.43	94	0.07	18.55	456	2.7	
CC27819		0.93	3.69	105	0.08	20.90	444	3.1	
CC27820		0.81	4.49	242	0.11	20.10	556	3.7	
CC27821		1.32	7.20	311	0.17	25.50	1090	6.6	
CC27822		0.58	6.60	279	0.16	23.60	583	11.5	
CC27823		1.27	4.98	694	0.26	15.20	197	0.6	
CC27824		0.43	5.26	178	0.10	22.00	453	2.4	
CC27825		0.27	2.69	78	0.08	20.10	180	2.4	
CC27826		0.17	2.09	72	0.06	17.10	126	2.2	
CC27827		4.32	17.90	1350	0.31	25.60	985	1.5	
CC27828		1.02	1.10	163	0.17	20.10	420	2.1	
CC27829		1.18	1.91	192	0.12	17.40	295	1.8	
CC27830		2.72	2.08	115	0.17	6.69	130	1.3	
CC27831		0.43	1.26	153	0.11	24.40	339	3.2	
CC27832		0.21	1.07	121	0.08	16.40	237	2.2	
CC27833		0.20	1.31	108	0.08	16.55	298	2.9	
CC27834		1.95	1.30	363	0.21	2.90	217	<0.5	
CC27835		1.37	2.19	226	0.17	11.05	354	1.7	
CC27836		2.05	2.60	291	0.25	17.80	480	0.6	
CC27837		0.85	1.14	138	0.13	2.00	29	<0.5	
CC27838		1.65	6.14	394	0.25	26.10	875	3.6	
CC27839		1.45	1.62	450	0.22	2.92	58	0.7	
CC27840		1.23	4.76	157	0.18	5.85	34	0.8	
CC27841		0.76	1.47	94	0.09	3.95	40	<0.5	
CC27842		0.85	7.06	120	0.13	7.29	21	<0.5	
CC27843		2.35	4.81	219	0.31	7.46	29	0.5	
CC27844		4.08	3.54	178	0.35	6.15	35	<0.5	
CC27845		2.18	1.26	105	0.26	2.15	31	<0.5	
CC27846		1.08	3.01	96	0.13	15.35	145	1.4	
CC27847		1.08	2.59	166	0.21	13.70	329	1.2	
CC27848		1.95	2.47	354	0.27	10.40	399	0.6	
CC27849		0.53	5.04	265	0.12	21.00	783	3.0	

Comments: Gold determinations by ME-MS41 are semi-quantitative due to the small sample weight used (0.5g).

ALS Chemex

EXCELLENCE IN ANALYTICAL CHEMISTRY

ALS Canada Ltd.

212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: STRATEGIC METALS LTD.
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO

Finalized Date: 25-SEP-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07098782

Sample Description	Method / Analyte / Units / LOR	WEI-21 Recvd Wt. kg 0.02	ME-MS41 Ag ppm 0.01	ME-MS41 Al % 0.01	ME-MS41 As ppm 0.1	ME-MS41 Au ppm 0.2	ME-MS41 B ppm 10	ME-MS41 Ba ppm 10	ME-MS41 Be ppm 0.05	ME-MS41 Bi ppm 0.01	ME-MS41 Ca % 0.01	ME-MS41 Cd ppm 0.01	ME-MS41 Ce ppm 0.02	ME-MS41 Co ppm 0.1	ME-MS41 Cr ppm 1	ME-MS41 Cs ppm 0.05
CC27850		0.24	0.74	1.17	20.5	<0.2	<10	3010	0.71	0.19	0.28	3.40	32.40	6.8	40	0.77
CC27851		0.32	1.52	1.04	20.5	<0.2	<10	400	0.37	0.31	0.08	0.50	23.70	2.1	23	0.76
CC27852		0.28	0.62	1.41	13.4	<0.2	<10	760	0.49	0.23	0.15	0.79	28.60	4.9	27	0.71
CC27853		0.34	0.51	1.37	9.8	<0.2	<10	870	0.50	0.20	0.13	0.70	28.50	3.7	24	0.85
CC27854		0.38	0.38	1.38	11.3	<0.2	<10	1040	0.49	0.19	0.27	0.64	33.40	7.6	24	0.84
CC27855		0.50	0.41	1.55	8.8	<0.2	<10	1280	0.60	0.20	0.35	0.64	33.60	8.0	27	0.94
CC27856		0.26	0.43	1.73	11.7	<0.2	<10	2150	0.89	0.20	0.66	0.42	38.40	12.7	29	0.96
CC27857		0.12	0.30	0.81	6.5	<0.2	<10	280	0.43	0.15	3.32	0.89	36.70	7.0	12	1.06
CC27858		0.16	0.33	0.86	6.0	<0.2	<10	270	0.44	0.16	3.04	1.05	40.20	7.2	13	1.15
CC27859		0.14	0.28	0.82	5.3	<0.2	<10	260	0.36	0.14	2.61	0.81	41.20	6.5	12	1.05
CC27860		0.24	0.27	0.69	7.6	<0.2	<10	460	0.36	0.14	5.41	0.78	35.70	7.8	12	0.89
CC27861		0.20	0.24	0.73	6.5	<0.2	<10	350	0.39	0.13	4.72	0.74	38.90	7.1	12	0.97
CC27881		0.40	0.32	1.44	10.2	<0.2	<10	1070	0.55	0.20	0.89	1.78	39.90	13.5	27	0.85
CC27882		0.32	0.29	1.51	9.9	<0.2	<10	1150	0.51	0.21	0.31	1.16	38.40	10.3	27	0.83
CC27883		0.44	0.26	1.43	13.9	<0.2	<10	640	0.50	0.21	2.37	1.63	41.30	15.8	25	1.14
CC27884		0.48	0.33	1.45	12.6	<0.2	<10	1320	0.58	0.21	0.32	1.93	39.80	10.5	27	0.79
CC27885		0.18	0.36	1.44	11.5	<0.2	<10	1260	0.51	0.21	0.46	1.93	37.10	11.4	26	0.76
CC27886		0.26	0.30	1.44	13.4	<0.2	<10	1180	0.58	0.20	0.58	2.08	38.60	12.6	26	0.87
CC27887		0.14	2.09	0.52	53.6	<0.2	10	660	0.59	0.16	2.55	18.65	17.65	7.4	46	0.70
CC27888		0.10	2.00	0.62	67.1	<0.2	20	630	0.74	0.21	2.01	22.30	15.65	10.3	42	0.77
CC27889		0.22	4.35	0.82	92.0	<0.2	20	730	0.84	0.26	5.30	45.40	21.50	9.6	53	1.38
CC27890		0.06	5.42	1.27	97.1	<0.2	20	750	1.30	0.30	2.25	49.10	37.90	11.1	110	1.94
CC27891		0.10	6.63	0.83	87.5	<0.2	10	780	1.06	0.25	1.70	38.20	35.30	8.2	102	1.26
CC27892		0.10	4.07	0.77	57.5	<0.2	10	900	0.82	0.15	3.34	35.40	27.60	4.7	68	1.01
CC27893		0.04	2.89	0.73	44.2	<0.2	10	770	0.75	0.14	3.44	41.30	22.40	4.3	53	0.90
CC27894		0.12	1.88	0.69	28.5	<0.2	<10	590	0.51	0.11	2.73	30.60	12.90	4.1	33	0.69
CC27895		0.12	0.34	0.54	16.7	<0.2	<10	490	0.55	0.16	0.43	2.17	12.05	11.3	9	0.45
CC27896		0.10	1.13	0.38	11.8	<0.2	<10	410	0.22	0.13	0.20	0.99	6.83	0.7	11	0.42
CC27897		0.12	0.84	0.66	10.4	<0.2	<10	230	0.26	0.19	0.02	0.37	6.30	0.4	16	0.56
CC27898		0.10	0.28	0.52	10.7	<0.2	<10	150	0.11	0.22	0.11	0.65	20.30	2.0	12	0.54
CC27899		0.10	0.80	0.37	3.0	<0.2	<10	130	0.15	0.10	0.04	0.48	8.73	0.7	10	0.67
CC27900		0.12	0.72	0.75	14.8	<0.2	<10	110	0.13	0.21	0.02	0.22	9.23	1.7	15	0.65
CC27901		0.08	0.40	0.56	7.9	<0.2	<10	310	0.24	0.18	0.12	0.94	11.50	2.0	11	0.69
CC27902		0.20	0.29	0.56	10.4	<0.2	<10	180	0.22	0.14	0.03	0.38	4.48	0.7	9	0.44
CC27903		0.18	0.08	1.36	18.5	<0.2	<10	240	0.26	0.25	0.04	0.35	18.50	4.7	22	0.72
CC27904		0.16	0.07	0.36	29.7	<0.2	<10	80	0.17	0.14	0.01	0.31	2.94	3.9	11	0.57
CC27905		0.14	0.14	0.36	40.3	<0.2	<10	130	0.14	0.13	0.05	0.49	4.60	3.9	14	0.51
CC27906		0.02	1.15	0.54	26.8	<0.2	<10	170	0.22	0.15	0.09	1.60	15.30	1.7	40	0.85
CC27907		0.04	1.22	2.43	44.9	<0.2	<10	1440	1.40	0.25	0.72	8.11	43.00	11.9	73	1.24
CC27908		0.12	2.22	0.73	70.5	<0.2	10	680	0.93	0.24	2.37	23.80	16.85	9.0	42	0.60

Comments: Gold determinations by ME-MS41 are semi-quantitative due to the small sample weight used (0.5g).

ALS Chemex

EXCELLENCE IN ANALYTICAL CHEMISTRY

ALS Canada Ltd.

212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO

Finalized Date: 25-SEP-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07098782

Sample Description	Method	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41
	Analyte	Cu	Fe	Ga	Ge	Hf	Hg	In	K	La	Li	Mg	Mn	Mo	Na	Nb
	Units	ppm	%	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	%	ppm	ppm	%	ppm
	LOR	0.2	0.01	0.05	0.05	0.02	0.01	0.005	0.01	0.2	0.1	0.01	5	0.05	0.01	0.05
CC27850		46.0	2.10	4.44	0.07	0.03	0.16	0.031	0.07	17.5	10.0	0.20	126	14.45	0.02	0.54
CC27851		33.7	1.84	4.15	0.08	0.02	0.32	0.033	0.08	11.9	7.6	0.18	41	25.20	0.01	0.61
CC27852		30.6	2.17	4.95	0.07	0.02	0.13	0.037	0.08	14.5	12.6	0.25	78	14.70	0.01	0.71
CC27853		29.8	1.61	4.66	0.08	0.03	0.09	0.033	0.07	14.1	11.1	0.21	52	10.35	0.01	0.72
CC27854		28.4	2.33	4.64	0.06	0.05	0.05	0.033	0.07	16.0	13.2	0.28	131	7.65	0.02	0.84
CC27855		27.8	2.02	5.21	0.07	0.05	0.07	0.036	0.08	16.4	14.5	0.30	105	5.48	0.02	0.85
CC27856		39.8	2.47	5.43	0.07	0.08	0.08	0.038	0.08	19.0	16.0	0.41	287	5.15	0.02	0.82
CC27857		22.6	1.77	2.25	0.06	0.09	0.05	0.023	0.06	18.8	25.3	1.89	158	1.73	0.02	0.14
CC27858		23.8	1.72	2.48	0.05	0.10	0.06	0.023	0.07	20.0	26.0	1.67	161	1.52	0.02	0.17
CC27859		19.4	1.66	2.29	0.05	0.08	0.05	0.020	0.07	20.4	25.3	1.60	143	1.39	0.01	0.13
CC27860		24.5	1.85	2.01	0.05	0.11	0.03	0.022	0.07	18.3	19.8	2.93	198	2.41	0.02	0.08
CC27861		19.9	1.77	2.04	0.05	0.08	0.03	0.020	0.07	19.4	21.8	2.67	180	1.92	0.02	0.10
CC27881		32.6	2.94	4.68	0.06	0.08	0.02	0.037	0.10	19.7	15.5	0.60	361	3.76	0.02	0.73
CC27882		26.8	2.63	4.92	0.06	0.03	0.04	0.036	0.08	19.3	14.5	0.39	165	3.32	0.02	0.65
CC27883		33.3	3.49	4.75	0.06	0.14	0.03	0.040	0.13	19.6	17.2	1.15	562	2.70	0.02	0.62
CC27884		27.8	3.09	4.84	0.06	0.07	0.04	0.037	0.09	20.0	13.9	0.38	120	2.31	0.02	0.72
CC27885		27.6	2.93	4.65	0.06	0.02	0.04	0.037	0.08	18.4	13.1	0.36	252	5.26	0.02	0.60
CC27886		28.4	3.52	4.68	0.06	0.04	0.04	0.039	0.08	19.0	14.1	0.44	431	6.07	0.02	0.67
CC27887		68.6	1.26	3.02	0.08	0.07	0.37	0.027	0.07	9.2	3.0	0.15	169	29.50	0.02	0.20
CC27888		79.3	1.97	3.37	0.08	0.10	0.27	0.038	0.10	9.2	3.1	0.18	149	43.60	0.02	0.23
CC27889		131.0	1.77	5.19	0.10	0.12	0.50	0.045	0.15	10.8	3.0	0.85	111	43.50	0.02	0.21
CC27890		139.0	1.84	6.71	0.15	0.06	0.58	0.046	0.15	24.5	4.8	0.29	104	72.40	0.02	0.35
CC27891		139.0	1.76	4.66	0.17	0.08	0.87	0.038	0.11	24.5	3.8	0.12	95	49.60	0.02	0.27
CC27892		97.5	1.15	3.49	0.15	0.09	0.63	0.026	0.08	27.6	3.9	0.16	88	45.90	0.02	0.34
CC27893		84.6	0.98	3.14	0.12	0.08	0.43	0.025	0.06	18.1	3.5	0.13	134	25.50	0.03	0.32
CC27894		64.7	1.01	2.64	0.09	0.07	0.39	0.023	0.05	8.8	3.7	0.14	176	13.25	0.02	0.34
CC27895		24.1	2.11	1.74	0.08	0.06	0.10	0.025	0.05	6.5	1.8	0.04	268	38.60	0.01	0.15
CC27896		30.8	0.89	1.92	0.06	0.02	0.12	0.018	0.10	4.1	0.6	0.02	11	25.60	0.01	0.12
CC27897		27.0	0.95	3.30	0.05	0.03	0.10	0.014	0.08	3.7	1.1	0.03	9	13.40	0.01	0.17
CC27898		14.0	1.07	6.39	0.05	<0.02	0.02	0.011	0.03	10.7	0.8	0.03	46	13.50	0.01	0.35
CC27899		9.5	0.45	2.35	<0.05	<0.02	0.04	0.009	0.05	4.9	0.4	0.02	12	4.90	0.01	0.16
CC27900		10.6	2.04	4.65	0.05	0.04	0.05	0.018	0.05	5.2	3.0	0.07	54	21.40	0.01	0.81
CC27901		17.0	0.97	3.75	<0.05	<0.02	0.05	0.015	0.04	6.2	0.9	0.03	46	12.05	0.02	0.38
CC27902		19.1	0.90	2.01	<0.05	0.03	0.04	0.017	0.07	2.5	2.0	0.04	41	32.30	0.01	0.19
CC27903		16.6	3.07	6.63	0.07	0.04	0.02	0.025	0.05	9.8	9.0	0.17	126	21.80	0.01	1.00
CC27904		21.7	1.41	2.66	0.05	0.02	0.01	0.019	0.04	1.9	0.4	0.02	28	63.70	0.01	0.17
CC27905		24.6	1.43	2.74	0.07	<0.02	0.02	0.021	0.03	2.7	0.4	0.02	20	69.90	0.01	0.19
CC27906		24.9	1.04	5.65	0.08	<0.02	0.05	0.014	0.05	9.5	1.2	0.04	30	32.70	0.01	0.34
CC27907		43.2	2.83	7.45	0.13	0.11	0.11	0.046	0.08	17.3	14.6	0.28	207	45.80	0.03	0.76
CC27908		106.5	2.18	3.84	0.14	0.13	0.38	0.038	0.10	9.1	3.6	0.90	115	66.40	0.02	0.21

Comments: Gold determinations by ME-MS41 are semi-quantitative due to the small sample weight used (0.5g).

ALS Chemex

EXCELLENCE IN ANALYTICAL CHEMISTRY

ALS Canada Ltd.

212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: STRATEGIC METALS LTD.
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO

Finalized Date: 25-SEP-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07098782

Sample Description	Method	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41
	Analyte	Ni	P	Pb	Rb	Re	S	Sb	Sc	Se	Sn	Sr	Ta	Te	Th	Ti
	Units	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%
	LOR	0.2	10	0.2	0.1	0.001	0.01	0.05	0.1	0.2	0.2	0.2	0.01	0.01	0.2	0.005
CC27850		70.1	580	11.3	12.0	0.008	0.06	4.20	4.3	4.3	0.7	45.6	<0.01	0.09	3.0	0.009
CC27851		14.8	640	18.2	11.5	0.005	0.04	11.00	3.0	9.8	0.9	34.5	<0.01	0.19	2.2	0.012
CC27852		27.8	550	13.5	12.1	0.001	0.03	4.17	3.8	6.1	0.7	39.0	<0.01	0.09	2.4	0.013
CC27853		29.8	420	11.7	12.6	0.001	0.03	3.31	4.3	6.5	0.7	34.5	<0.01	0.09	3.1	0.012
CC27854		24.6	480	10.9	12.2	0.001	0.02	2.03	4.9	2.4	0.6	30.3	<0.01	0.06	4.3	0.015
CC27855		30.4	430	12.2	14.1	0.002	0.03	1.98	5.2	2.7	0.6	35.7	<0.01	0.07	4.4	0.013
CC27856		53.6	650	12.2	13.9	0.001	0.05	1.95	5.6	2.3	0.6	50.9	<0.01	0.07	4.4	0.012
CC27857		20.8	850	26.4	7.0	0.002	0.07	0.83	2.0	1.3	0.2	53.1	<0.01	0.03	4.9	<0.005
CC27858		20.9	870	25.6	8.0	0.002	0.08	0.83	2.2	1.4	0.2	56.8	<0.01	0.03	4.3	<0.005
CC27859		18.7	800	22.3	7.3	0.001	0.05	0.73	1.9	1.2	0.2	41.4	<0.01	0.03	4.7	<0.005
CC27860		24.7	830	23.7	6.3	0.003	0.05	1.02	2.1	1.4	0.2	74.3	<0.01	0.03	5.0	<0.005
CC27861		21.2	800	20.0	6.3	0.002	0.05	0.90	1.9	1.1	0.2	60.5	<0.01	0.03	4.6	<0.005
CC27881		40.1	740	11.9	13.5	0.002	0.10	1.01	5.2	1.7	0.5	52.1	<0.01	0.05	5.6	0.014
CC27882		33.2	680	12.5	14.8	0.002	0.08	0.88	4.9	1.7	0.5	30.7	<0.01	0.05	4.8	0.009
CC27883		44.0	820	13.5	15.0	0.001	0.05	0.94	5.6	1.8	0.6	62.2	<0.01	0.05	6.9	0.022
CC27884		36.7	760	13.5	15.5	0.003	0.09	0.94	5.3	1.8	0.6	37.0	<0.01	0.05	5.6	0.010
CC27885		37.8	850	13.1	14.0	0.003	0.11	0.97	5.0	1.8	0.5	42.1	<0.01	0.05	4.5	0.008
CC27886		38.8	880	13.0	12.8	0.002	0.11	0.97	5.6	1.8	0.5	41.0	<0.01	0.06	5.4	0.010
CC27887		163.0	680	12.0	9.8	0.021	0.14	19.80	2.9	10.9	0.7	136.5	<0.01	0.16	0.8	0.005
CC27888		252.0	590	14.6	11.4	0.015	0.12	22.70	4.0	11.3	0.9	89.8	<0.01	0.18	1.4	0.005
CC27889		278.0	790	18.8	17.9	0.013	0.06	27.10	7.0	12.9	1.0	194.5	<0.01	0.18	4.2	0.006
CC27890		270.0	960	22.0	16.8	0.008	0.08	29.30	5.7	24.3	1.1	155.5	<0.01	0.32	1.9	0.012
CC27891		258.0	870	18.5	15.5	0.008	0.11	29.40	5.4	28.3	0.8	134.5	<0.01	0.30	1.7	0.008
CC27892		191.0	980	12.2	11.1	0.015	0.19	31.40	3.7	23.3	0.5	183.0	<0.01	0.19	0.7	0.009
CC27893		180.0	930	10.4	8.1	0.013	0.17	26.50	2.6	16.7	0.5	209.0	<0.01	0.15	0.5	0.008
CC27894		166.5	800	7.4	6.9	0.020	0.17	13.95	2.6	15.0	0.4	160.0	<0.01	0.10	0.5	0.008
CC27895		68.1	390	9.1	8.0	0.016	0.05	2.85	2.7	5.2	0.4	50.0	<0.01	0.07	1.3	<0.005
CC27896		17.3	400	8.9	7.5	0.004	0.21	14.15	1.3	8.2	0.5	52.0	<0.01	0.10	0.6	<0.005
CC27897		4.7	170	11.7	7.8	0.002	0.09	5.44	2.0	4.0	0.6	17.9	<0.01	0.14	1.3	<0.005
CC27898		15.0	220	7.9	3.9	<0.001	0.01	2.93	0.7	2.2	0.9	11.0	<0.01	0.09	<0.2	0.016
CC27899		4.4	380	5.3	5.1	<0.001	0.03	1.88	0.7	1.3	0.5	7.6	<0.01	0.04	0.3	0.008
CC27900		6.5	210	11.7	9.1	<0.001	0.03	12.85	1.4	2.9	0.6	10.9	<0.01	0.08	1.6	0.017
CC27901		12.6	410	10.1	5.9	<0.001	0.05	2.18	0.9	1.9	0.7	16.6	<0.01	0.06	<0.2	0.017
CC27902		7.2	250	7.8	8.1	0.001	0.09	6.66	1.2	3.2	0.5	11.5	<0.01	0.09	0.8	0.005
CC27903		38.1	210	13.2	11.0	<0.001	0.02	2.73	2.2	2.4	0.8	11.5	<0.01	0.07	2.7	0.017
CC27904		146.0	100	5.6	7.6	0.001	0.01	7.87	1.2	4.0	0.5	1.8	<0.01	0.13	0.6	0.005
CC27905		194.5	220	5.2	4.6	0.003	0.02	10.80	1.1	7.1	0.7	4.6	<0.01	0.15	0.2	0.005
CC27906		56.8	330	8.9	6.9	0.001	0.03	22.90	1.3	9.1	0.7	9.0	<0.01	0.14	0.4	0.013
CC27907		170.5	460	17.9	12.6	0.001	0.04	17.20	5.1	10.5	0.9	34.5	<0.01	0.15	3.0	0.009
CC27908		271.0	850	14.6	9.6	0.004	0.04	22.50	6.5	10.6	0.9	103.5	0.01	0.17	2.7	0.005

Comments: Gold determinations by ME-MS41 are semi-quantitative due to the small sample weight used (0.5g).

ALS Chemex

EXCELLENCE IN ANALYTICAL CHEMISTRY

ALS Canada Ltd.

212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: STRATEGIC METALS LTD.
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO

Finalized Date: 25-SEP-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07098782

Sample Description	Method / Analyte / Units / LOR	ME-MS41 Tl ppm 0.02	ME-MS41 U ppm 0.05	ME-MS41 V ppm 1	ME-MS41 W ppm 0.05	ME-MS41 Y ppm 0.05	ME-MS41 Zn ppm 2	ME-MS41 Zr ppm 0.5	Zn-OG46 Zn % 0.01
CC27850		0.62	5.60	406	0.18	18.05	276	1.4	
CC27851		1.76	4.07	327	0.25	7.17	51	0.9	
CC27852		0.85	3.39	187	0.15	9.19	98	0.7	
CC27853		0.80	4.08	153	0.14	10.75	138	1.4	
CC27854		0.45	1.89	112	0.14	9.94	101	3.2	
CC27855		0.52	2.49	130	0.14	10.90	125	3.0	
CC27856		0.33	1.78	133	0.14	17.00	196	3.8	
CC27857		0.11	0.94	20	<0.05	12.70	149	5.1	
CC27858		0.12	0.95	21	<0.05	11.55	147	5.2	
CC27859		0.11	0.87	19	<0.05	11.65	136	4.4	
CC27860		0.09	1.09	23	<0.05	10.35	159	6.3	
CC27861		0.10	0.93	20	<0.05	11.95	143	5.6	
CC27881		0.18	1.58	64	0.07	13.75	149	4.5	
CC27882		0.20	1.69	67	0.09	12.05	132	1.7	
CC27883		0.19	1.36	47	0.07	14.55	141	7.3	
CC27884		0.19	2.02	72	0.10	13.30	158	3.4	
CC27885		0.19	2.07	69	0.12	13.30	179	1.2	
CC27886		0.18	1.08	67	0.12	13.70	187	1.9	
CC27887		0.92	12.90	812	0.23	24.90	1400	4.4	
CC27888		1.41	5.73	943	0.34	31.40	1620	5.1	
CC27889		1.34	8.85	1410	0.28	42.00	3270	8.5	
CC27890		2.21	7.26	2550	0.45	51.10	2980	3.3	
CC27891		2.03	7.58	1625	0.39	47.20	2480	4.5	
CC27892		2.03	15.95	1340	0.30	51.60	2170	5.6	
CC27893		1.86	12.10	985	0.21	36.10	2070	4.5	
CC27894		1.72	10.15	502	0.16	22.70	1870	4.1	
CC27895		0.87	1.57	125	0.13	16.75	151	1.2	
CC27896		1.50	2.21	148	0.18	5.20	44	<0.5	
CC27897		1.15	3.08	154	0.15	3.05	17	1.2	
CC27898		0.28	0.65	163	0.17	1.83	61	<0.5	
CC27899		0.51	0.88	103	0.08	1.60	16	<0.5	
CC27900		0.90	0.60	282	0.20	1.46	25	1.4	
CC27901		0.18	0.80	110	0.13	1.97	38	<0.5	
CC27902		1.77	2.32	209	0.16	3.14	24	0.8	
CC27903		0.53	0.69	252	0.17	2.64	160	2.0	
CC27904		1.50	0.72	535	0.23	3.05	333	1.3	
CC27905		2.06	1.07	318	0.30	2.65	295	<0.5	
CC27906		0.85	1.03	719	0.23	2.42	274	<0.5	
CC27907		1.42	2.84	1130	0.26	20.30	877	3.4	
CC27908		1.32	6.50	894	0.31	43.20	1880	3.9	

Comments: Gold determinations by ME-MS41 are semi-quantitative due to the small sample weight used (0.5g).

ALS Chemex

EXCELLENCE IN ANALYTICAL CHEMISTRY

ALS Canada Ltd.

212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO

Finalized Date: 25-SEP-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07098782

Sample Description	Method	WEI-21	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41
	Analyte	Recvd Wt.	Ag	Al	As	Au	B	Ba	Be	Bi	Ca	Cd	Ce	Co	Cr	Cs
	Units	kg	ppm	%	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppm	ppm	ppm
	LOR	0.02	0.01	0.01	0.1	0.2	10	10	0.05	0.01	0.01	0.01	0.02	0.1	1	0.05
CC27909		0.10	4.29	0.54	29.6	<0.2	<10	650	0.93	0.18	3.29	12.80	27.20	6.5	142	0.42
CC27910		0.16	0.33	0.72	59.1	<0.2	<10	790	0.89	0.23	0.55	12.30	23.10	7.2	51	0.75
CC27911		0.16	0.62	0.53	41.7	<0.2	<10	760	0.38	0.20	0.12	3.40	18.75	3.2	37	0.78
CC27912		0.12	0.51	0.93	6.7	<0.2	<10	5610	0.65	0.17	0.49	2.69	34.60	7.3	22	0.51
CC27913		0.22	0.91	1.21	14.9	<0.2	<10	4660	0.53	0.24	0.49	1.12	29.80	37.9	23	0.70
CC27914		0.10	2.27	0.72	28.9	<0.2	<10	960	0.80	0.11	3.52	55.90	18.15	5.6	35	0.61
CC27915		0.06	0.93	0.41	17.7	<0.2	<10	270	0.20	0.13	0.50	5.31	8.94	1.6	34	0.52
CC27916		0.12	0.94	1.44	92.2	<0.2	10	2370	0.82	0.28	1.38	2.36	13.75	3.6	24	0.62
CC27917		0.32	0.41	1.21	8.1	<0.2	<10	2180	0.56	0.19	0.28	4.81	34.50	7.3	26	0.58
CC27918		0.18	0.33	1.27	11.4	<0.2	<10	1770	0.58	0.21	0.16	2.06	35.80	6.2	26	0.70
CC27919		0.26	0.31	1.16	8.0	<0.2	<10	1690	0.52	0.20	0.13	2.15	35.40	4.4	25	0.68
CC27920		0.40	0.38	1.26	16.6	<0.2	<10	1910	0.61	0.21	0.17	2.44	35.50	5.4	26	0.71
CC27921		0.26	0.30	1.24	19.7	<0.2	<10	1440	0.51	0.22	0.15	1.17	34.00	4.5	26	0.64
CC27922		0.14	1.57	0.46	3.9	<0.2	<10	1590	0.3	0.1	0.09	5.49	10.05	0.6	41	0.98
CC27923		0.16	0.91	0.41	3	<0.2	<10	1190	0.27	0.06	0.06	2.69	16.8	0.4	35	0.87
CC27924		0.12	1.21	0.47	3.7	<0.2	<10	2580	0.35	0.1	0.13	5.77	10.7	0.8	31	0.68
CC27925		0.10	0.89	0.5	3.4	<0.2	<10	1320	0.3	0.08	0.1	2.8	13.9	0.6	30	0.63
CC27927		0.20	0.36	0.97	5.0	<0.2	<10	1920	0.41	0.16	0.30	0.91	23.70	3.8	16	0.57
CC27928		0.06	0.65	1.10	6.1	<0.2	10	370	0.73	0.11	2.24	4.04	25.50	6.5	21	0.92
CC27929		0.32	1.43	2.30	101.0	<0.2	<10	670	0.74	0.23	0.09	7.35	11.45	2.8	110	1.89
CC27930		0.42	0.55	3.25	77.4	<0.2	<10	480	0.83	0.30	0.06	4.58	19.50	7.0	80	2.50
CC27931		0.40	2.38	2.46	166.5	<0.2	10	240	1.55	0.34	0.17	33.30	15.00	9.5	150	3.17
CC27932		0.38	1.89	2.18	99.4	<0.2	<10	1440	1.51	0.27	0.59	139.00	29.30	29.1	99	2.98
CC27933		0.40	3.73	2.12	88.9	<0.2	<10	750	1.15	0.29	1.00	171.50	36.00	35.2	80	3.02
CC27934		0.40	6.44	2.85	144.5	<0.2	<10	590	1.28	0.33	0.76	150.00	22.30	36.9	118	2.78
CC27935		0.30	2.08	1.90	54.4	<0.2	<10	2210	0.88	0.26	0.58	53.00	24.40	13.7	66	1.50
CC27936		0.40	3.31	1.63	46.7	<0.2	<10	2970	0.76	0.24	0.28	26.60	27.70	14.8	59	1.17
CC27937		0.24	6.40	1.07	36.1	<0.2	<10	2560	0.64	0.18	0.54	29.60	14.30	7.2	87	1.13
CC27938		0.16	2.29	0.44	13.2	<0.2	<10	1220	0.37	0.10	1.43	15.60	9.31	2.6	21	0.47

Comments: Gold determinations by ME-MS41 are semi-quantitative due to the small sample weight used (0.5g).

ALS Chemex
EXCELLENCE IN ANALYTICAL CHEMISTRY
ALS Canada Ltd.
212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: STRATEGIC METALS LTD.
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO

Finalized Date: 25-SEP-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07098782

Sample Description	Method	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41
	Analyte	Cu	Fe	Ga	Ge	Hf	Hg	In	K	La	Li	Mg	Mn	Mo	Na	Nb
	Units	ppm	%	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	%	ppm	ppm	%	ppm
	LOR	0.2	0.01	0.05	0.05	0.02	0.01	0.005	0.01	0.2	0.1	0.01	5	0.05	0.01	0.05
CC27909		133.5	1.51	2.98	0.16	0.14	0.72	0.028	0.05	20.0	3.2	0.84	208	18.70	0.03	0.22
CC27910		89.4	1.89	5.53	0.11	0.04	0.14	0.035	0.05	13.7	4.3	0.09	80	77.70	0.02	0.28
CC27911		55.5	1.49	4.81	0.08	0.02	0.12	0.019	0.04	11.6	1.8	0.04	43	72.00	0.02	0.34
CC27912		42.4	1.21	3.30	0.09	0.10	0.28	0.030	0.05	19.5	6.5	0.16	147	7.82	0.10	0.28
CC27913		27.7	4.49	4.16	0.12	0.07	0.25	0.036	0.06	15.3	7.8	0.21	1670	75.50	0.09	0.35
CC27914		79.3	0.90	2.67	0.14	0.10	0.31	0.018	0.04	18.3	2.9	0.10	283	22.20	0.04	0.32
CC27915		37.2	0.69	3.00	0.06	<0.02	0.10	0.015	0.04	6.1	0.6	0.04	27	15.15	0.02	0.20
CC27916		47.9	2.41	5.13	0.16	0.14	0.42	0.057	0.13	7.8	3.9	0.14	87	51.40	0.06	0.34
CC27917		34.3	2.04	4.41	0.09	0.06	0.08	0.029	0.08	19.1	10.5	0.30	137	7.28	0.04	0.48
CC27918		29.9	2.04	4.66	0.08	0.06	0.07	0.030	0.07	19.6	11.8	0.28	76	2.68	0.03	0.51
CC27919		26.3	1.70	4.33	0.08	0.04	0.07	0.029	0.07	19.7	11.4	0.26	49	1.69	0.03	0.49
CC27920		31.1	2.69	4.55	0.09	0.05	0.08	0.032	0.07	19.5	11.2	0.26	69	5.87	0.04	0.50
CC27921		24.5	2.93	4.46	0.09	0.07	0.07	0.028	0.06	18.7	12.2	0.29	62	13.30	0.03	0.53
CC27922		42.4	0.2	2.32	0.09	0.03	0.26	0.017	0.03	6.6	1	0.03	11	3.4	0.03	1.09
CC27923		24.5	0.12	2.81	0.07	<0.02	0.24	0.011	0.04	10.5	1	0.02	7	1.23	0.02	0.68
CC27924		58	0.34	2.93	0.06	<0.02	0.12	0.015	0.04	6.9	1.2	0.03	13	3.2	0.05	0.41
CC27925		23.7	0.23	3.06	0.06	<0.02	0.18	0.013	0.04	8.4	1.5	0.03	9	1.08	0.03	0.46
CC27927		25.1	1.34	3.27	0.07	0.04	0.09	0.024	0.06	12.5	8.6	0.20	65	2.26	0.04	0.45
CC27928		47.7	1.31	3.46	0.10	0.14	0.21	0.024	0.12	14.9	18.5	0.87	240	1.67	0.03	0.43
CC27929		285.0	1.95	6.78	0.16	0.05	0.48	0.092	0.11	7.5	3.5	0.08	60	49.90	0.02	0.62
CC27930		93.3	3.72	9.88	0.12	0.10	0.14	0.083	0.12	10.8	16.2	0.31	170	47.40	0.02	0.94
CC27931		308.0	3.62	9.55	0.36	0.10	0.36	0.094	0.28	9.8	7.3	0.15	236	154.50	0.02	1.07
CC27932		297.0	2.60	8.02	0.25	0.28	0.32	0.074	0.16	14.9	11.1	0.23	685	81.70	0.02	0.65
CC27933		238.0	3.47	7.74	0.34	0.24	1.07	0.093	0.20	19.3	11.9	0.34	807	80.80	0.02	0.61
CC27934		265.0	4.11	7.27	0.36	0.37	0.95	0.121	0.20	11.8	8.7	0.25	656	89.90	0.02	0.59
CC27935		100.5	3.09	6.52	0.15	0.19	0.33	0.055	0.16	12.0	14.5	0.48	387	30.90	0.03	0.63
CC27936		85.9	2.88	5.82	0.13	0.07	0.36	0.051	0.13	13.7	13.1	0.36	416	29.70	0.03	0.69
CC27937		139.5	1.63	3.96	0.13	0.06	1.11	0.032	0.11	8.2	5.9	0.13	126	22.60	0.02	0.41
CC27938		73.8	0.90	1.74	0.16	0.09	0.44	0.022	0.04	5.3	1.5	0.13	54	12.10	0.02	0.17

Comments: Gold determinations by ME-MS41 are semi-quantitative due to the small sample weight used (0.5g).

ALS Chemex
EXCELLENCE IN ANALYTICAL CHEMISTRY
ALS Canada Ltd.
212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: STRATEGIC METALS LTD.
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO

Finalized Date: 25-SEP-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07098782

Sample Description	Method	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41
	Analyte	Ni	P	Pb	Rb	Re	S	Sb	Sc	Se	Sn	Sr	Ta	Te	Th	Ti
	Units	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%
	LOR	0.2	10	0.2	0.1	0.001	0.01	0.05	0.1	0.2	0.2	0.2	0.01	0.01	0.2	0.005
CC27909		175.5	1390	10.4	6.0	0.004	0.11	11.35	6.2	15.2	0.7	173.5	0.01	0.14	1.5	0.006
CC27910		207.0	520	14.4	9.1	0.001	0.05	16.60	2.7	8.4	1.0	43.8	<0.01	0.17	0.9	0.006
CC27911		134.0	340	11.6	7.6	0.001	0.04	18.70	1.3	7.8	0.8	17.2	<0.01	0.13	0.3	0.009
CC27912		58.2	630	9.6	7.7	0.007	0.08	1.58	3.8	3.1	0.7	69.9	0.01	0.05	1.9	0.006
CC27913		40.8	860	12.5	10.6	0.012	0.08	3.13	3.6	3.9	0.6	64.9	<0.01	0.08	2.1	0.005
CC27914		130.0	980	9.2	6.1	0.007	0.16	18.25	2.5	11.4	0.4	153.0	0.01	0.09	0.4	0.009
CC27915		31.5	750	9.7	3.2	0.003	0.08	16.50	1.1	6.6	0.5	44.4	<0.01	0.12	<0.2	0.008
CC27916		112.0	1320	17.1	14.3	0.044	0.18	7.81	4.7	26.1	1.1	225.0	<0.01	0.53	1.4	<0.005
CC27917		50.2	640	10.4	12.0	0.007	0.02	2.54	4.6	3.8	0.5	45.4	<0.01	0.06	4.8	0.009
CC27918		37.5	540	12.3	12.5	0.007	0.02	2.48	4.2	2.7	0.6	29.5	<0.01	0.06	5.1	0.007
CC27919		30.6	490	11.7	12.7	0.005	0.02	2.25	3.8	2.2	0.5	25.8	<0.01	0.05	4.9	0.008
CC27920		39.2	650	13.1	12.0	0.003	0.03	2.31	4.4	3.1	0.5	30.9	<0.01	0.06	5.0	0.007
CC27921		29.1	580	12.4	11.3	0.003	0.02	2.30	3.9	2.7	0.6	27.0	<0.01	0.06	5.1	0.008
CC27922		20.2	600	10.7	4.4	0.006	0.1	8.04	2.1	8.7	0.5	17.2	<0.01	0.1	<0.2	0.048
CC27923		13.2	330	7.6	5	0.007	0.06	4.14	1.4	6.2	0.4	13	<0.01	0.06	0.3	0.028
CC27924		36.6	760	10.3	4.3	0.004	0.11	3	0.5	4.4	0.5	39.1	<0.01	0.07	<0.2	0.015
CC27925		14.4	620	6.7	5.9	0.005	0.09	3.34	0.8	5.6	0.4	19.3	<0.01	0.05	<0.2	0.014
CC27927		21.2	550	9.6	9.1	0.007	0.06	0.88	3.3	2.9	0.4	30.5	<0.01	0.04	2.7	0.009
CC27928		40.3	1950	8.5	13.3	0.004	0.16	1.51	3.1	4.8	0.4	84.9	<0.01	0.04	1.7	0.010
CC27929		98.7	2660	13.8	19.4	0.019	0.23	20.70	2.8	23.5	1.0	90.3	0.01	0.23	0.3	0.012
CC27930		105.0	1590	16.2	20.1	0.007	0.08	13.30	6.4	9.1	1.4	41.1	0.01	0.18	3.3	0.015
CC27931		298.0	2050	26.0	21.7	0.013	0.51	95.00	9.7	48.6	1.5	211.0	0.01	0.47	2.3	0.062
CC27932		534.0	1590	28.9	22.9	0.004	0.18	27.10	7.6	31.6	1.3	94.5	0.02	0.29	1.4	0.021
CC27933		1255.0	1320	27.6	18.5	0.005	0.25	22.90	10.0	49.6	1.6	148.0	0.01	0.27	2.8	0.022
CC27934		1155.0	2010	29.7	18.9	0.009	0.31	31.10	9.0	50.7	2.2	160.5	0.02	0.38	2.9	0.021
CC27935		229.0	1010	20.7	17.4	0.003	0.17	10.50	5.5	15.2	1.1	96.8	0.01	0.15	1.7	0.016
CC27936		205.0	830	19.1	15.1	0.004	0.11	11.55	5.3	11.5	0.9	76.5	0.01	0.15	1.9	0.018
CC27937		193.5	1440	13.7	12.2	0.009	0.17	14.45	3.2	15.4	0.7	110.0	0.01	0.15	0.5	0.011
CC27938		159.0	1140	7.6	4.4	0.067	0.25	11.05	2.4	25.0	0.7	213.0	0.01	0.11	0.6	0.006

Comments: Gold determinations by ME-MS41 are semi-quantitative due to the small sample weight used (0.5g).

ALS Chemex

EXCELLENCE IN ANALYTICAL CHEMISTRY

ALS Canada Ltd.

212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO

Finalized Date: 25-SEP-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07098782

Sample Description	Method	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	Zn-OG46
	Analyte	Tl	U	V	W	Y	Zn	Zr	Zn
	Units	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%
	LOR	0.02	0.05	1	0.05	0.05	2	0.5	0.01
CC27909		0.79	4.41	302	0.26	35.60	1080	5.0	
CC27910		1.68	5.96	759	0.52	24.10	817	0.9	
CC27911		1.76	4.56	656	0.43	10.10	525	<0.5	
CC27912		0.59	7.34	145	0.12	23.20	123	2.9	
CC27913		0.51	3.69	236	0.17	15.25	126	1.4	
CC27914		1.05	10.30	572	0.15	44.90	1620	3.0	
CC27915		0.52	3.08	289	0.13	4.47	245	<0.5	
CC27916		6.55	5.82	279	0.19	12.05	209	4.6	
CC27917		0.28	2.99	174	0.10	15.10	393	1.7	
CC27918		0.31	2.56	180	0.11	13.00	237	1.7	
CC27919		0.28	2.09	168	0.08	10.90	188	1.3	
CC27920		0.29	2.99	170	0.11	14.00	203	1.5	
CC27921		0.26	2.25	160	0.09	10.85	167	2.1	
CC27922		1.01	4.73	572	0.05	8.61	117	1.1	
CC27923		0.96	2.72	400	0.05	6.47	71	0.5	
CC27924		0.84	4.76	326	<0.05	8.88	149	<0.5	
CC27925		0.87	2.51	342	0.05	5.7	91	<0.5	
CC27927		0.15	2.14	59	0.08	8.74	83	0.9	
CC27928		0.16	1.69	73	0.07	16.10	231	3.4	
CC27929		3.64	12.70	1205	0.50	16.15	218	1.7	
CC27930		3.16	11.65	1355	0.32	7.84	507	3.7	
CC27931		8.73	36.60	2660	0.91	46.50	1280	3.6	
CC27932		6.02	38.50	1935	0.71	91.10	6210	7.6	
CC27933		8.62	15.70	1295	0.66	69.70	>10000	7.3	2.15
CC27934		6.27	57.90	1695	0.78	89.70	>10000	14.4	1.47
CC27935		2.19	13.55	832	0.32	32.80	2840	4.7	
CC27936		1.67	7.25	716	0.31	23.90	2690	1.6	
CC27937		1.69	26.80	587	0.28	25.50	1605	1.3	
CC27938		0.49	8.87	173	0.16	18.35	1205	2.8	

Comments: Gold determinations by ME-MS41 are semi-quantitative due to the small sample weight used (0.5g).

ALS Chemex
EXCELLENCE IN ANALYTICAL CHEMISTRY
ALS Canada Ltd.
212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Finalized Date: 30-SEP-2007
Account: MTT

CERTIFICATE VA07098284

Project: NIMO RICH

P.O. No.: RI07-06

This report is for 28 Drill Core samples submitted to our lab in Vancouver, BC, Canada on 15-AUG-2007.

The following have access to data associated with this certificate:

AL ARCHER VANCOUVER OFFICE	DOUG EATON BILL WENGZYNOWSKI	JOAN MARIACHER

SAMPLE PREPARATION

ALS CODE	DESCRIPTION
WEI-21	Received Sample Weight
LOG-22	Sample login - Rcd w/o BarCode
CRU-31	Fine crushing - 70% <2mm
SPL-21	Split sample - riffle splitter
PUL-36	Pulverize 1.5 kg to 85% <75 um
CRU-QC	Crushing QC Test
BAG-01	Bulk Master for Storage

ANALYTICAL PROCEDURES

ALS CODE	DESCRIPTION	INSTRUMENT
Hg-CV41	Trace Hg - cold vapor/AAS	FIMS
ME-MS61	48 element four acid ICP-MS	

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

his is the Final Report and supersedes any preliminary report with this certificate number. Results apply to samples as submitted. All ges of this report have been checked and approved for release.

Signature: Lawrence Ng

Lawrence Ng, Laboratory Manager - Vancouver

ALS Chemex
EXCELLENCE IN ANALYTICAL CHEMISTRY
ALS Canada Ltd.
212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: STRATEGIC METALS LTD.
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO RICH

Finalized Date: 30-SEP-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07098284

Method	WEI-21	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61
Analyte	Recvd Wt.	Ag	Al	As	Ba	Be	Bi	Ca	Cd	Ce	Co	Cr	Cs	Cu	Fe
Units	kg	ppm	%	ppm	ppm	ppm	ppm	%	ppm	ppm	ppm	ppm	ppm	ppm	%
Sample Description LOR	0.02	0.01	0.01	0.2	10	0.05	0.01	0.01	0.02	0.01	0.1	1	0.05	0.2	0.01
C488171	2.36	0.4	2.11	14.5	510	1.15	0.07	0.08	3.51	15.2	5.7	43	2.37	42.3	1.27
C488172	2.60	0.34	2.1	12.3	370	1.18	0.03	0.1	3.46	17.75	4.9	40	2.5	39	1.31
C488173	1.76	0.65	2.15	16	420	1.12	0.03	0.66	12.5	15.65	5.7	47	2.46	63.4	1.72
C488174	1.58	0.51	1.76	14.5	540	1.11	0.08	0.08	9.53	13.6	4.3	51	2.19	44.1	1.36
C488175	0.90	0.31	1.42	12.7	1010	0.95	0.08	0.72	4.06	14.1	4.3	38	1.71	35.3	1.51
C488176	0.82	0.37	1.42	15.2	670	1.02	0.08	0.05	4.99	11.85	3.7	45	1.69	38.4	1.56
C488177	0.86	0.43	1.34	13.8	940	1.12	0.07	0.05	12	11.35	3.7	51	1.69	53.9	1.41
C488178	1.02	0.05	0.06	<5	20	0.1	0.02	19.85	0.1	1.29	0.9	1	0.17	1.4	0.42
C488179	0.46	0.8	2.35	27.1	280	1.55	0.12	0.92	10.5	18.05	6.5	80	2.49	84.5	2.5
C488181	0.66	0.09	0.06	<5	30	0.07	0.02	19.25	0.11	1.1	0.9	2	0.13	1.6	0.43
C488182	0.42	0.44	1.83	18.4	500	1.26	0.11	0.23	3.3	18.9	4.5	45	2.18	42.6	1.54
C488183	0.76	0.33	1.78	15.1	580	1.31	0.08	0.12	2.14	12.65	4.7	43	2.26	35.2	1.82
C488184	0.86	0.27	1.83	13	740	1.45	0.09	0.2	2.13	16.95	4.6	39	2.47	31.7	1.34
C488185	0.78	0.23	1.79	12.4	370	1.35	0.08	0.31	1.71	14.85	7.1	39	2.22	33.2	2.12
C488186	1.54	0.19	1.68	11.3	480	1.18	0.07	0.07	1.52	14.7	4.1	39	1.92	29.8	1.42
C488187	1.76	0.15	1.42	12.1	450	0.95	0.08	0.08	1.22	11.35	4.8	45	1.5	38.3	1.66
C488188	0.80	0.27	1.16	10.6	770	0.74	0.06	0.05	1.21	9.64	3.7	36	1.14	28	1.53
C488189	0.82	0.18	1.65	18.6	440	1.17	0.08	0.05	1.02	19	5	42	1.82	37.6	1.73
C488190	0.80	0.17	1.51	18.8	330	0.94	0.07	0.04	1.84	10.45	5.1	37	1.54	33.8	1.81
C488191	0.48	0.25	1.7	24.1	360	0.89	0.08	0.18	1.92	9.61	7.2	38	1.74	40	2.36
C488193	0.14	0.23	0.09	<5	60	0.08	0.02	19.45	0.08	1.2	1	3	0.13	4.3	0.48
C488194	0.44	0.38	6.46	71.6	200	2.96	0.22	0.23	3.13	30.4	14.6	90	9.14	52.4	3.69
C488195	0.96	0.2	3.68	36	130	1.55	0.17	16.8	1.73	22.4	8.4	32	5.19	26.2	1.84
C488196	0.76	0.26	3.85	24	310	1.44	0.11	20.5	2.88	42.2	7.8	36	4.61	32.2	1.84
C488197	1.80	0.34	5.3	34.3	160	1.73	0.16	1.85	4.83	38.5	10.6	58	6.4	39.9	2.76
C488198	1.82	0.26	4.11	18.3	280	1.32	0.13	5.75	3.94	39.4	8.2	50	4.66	26	2.04
C488199	2.08	0.3	5.72	23.1	120	1.87	0.17	2.38	3.73	42.5	10.9	55	6.8	33.6	2.6
C488200	2.66	0.29	4.79	21.7	130	1.68	0.14	1.84	3.34	33.7	9.5	51	5.94	32.9	2.38

Comments: Interference: Ca>10% on ICP-MS As,ICP-AES results shown. REE's may not be totally soluble in MS61 method.

ALS Chemex

EXCELLENCE IN ANALYTICAL CHEMISTRY

ALS Canada Ltd.

212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: STRATEGIC METALS LTD.
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO RICH

Finalized Date: 30-SEP-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07098284

Sample Description	Method	ME-MS61	ME-MS61	ME-MS61	Hg-CV41	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61
	Analyte	Ga	Ge	Hf	Hg	In	K	La	Li	Mg	Mn	Mo	Na	Nb	Ni	P
	Units	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	%	ppm	ppm	%	ppm	ppm	ppm
	LOR	0.05	0.05	0.1	0.01	0.005	0.01	0.5	0.2	0.01	5	0.05	0.01	0.1	0.2	10
C488171		5.57	0.1	0.8	0.09	0.016	0.68	9.9	6.9	0.13	62	41.5	0.05	3.8	138.5	140
C488172		5.85	0.11	0.9	0.09	0.015	0.68	12.7	6	0.14	61	48.6	0.04	3.7	127.5	260
C488173		6.17	0.15	0.8	0.14	0.023	0.67	10.1	5.9	0.38	110	37.2	0.06	3.7	127.5	160
C488174		5.19	0.13	0.8	0.11	0.018	0.59	9.3	6.2	0.12	61	41.5	0.03	3.2	125.5	170
C488175		4	0.14	0.7	0.08	0.017	0.45	9.8	5.6	0.38	125	44.8	0.03	2.8	121.5	820
C488176		3.87	0.12	0.7	0.09	0.016	0.45	8.6	6.4	0.09	69	52	0.03	2.9	149.5	180
C488177		4.15	0.14	0.7	0.10	0.021	0.42	7.1	5.5	0.09	67	44.7	0.03	2.6	145	170
C488178		0.29	0.19	<0.1	<0.01	0.008	0.03	0.7	1	12.8	191	0.51	<0.01	0.3	8.7	190
C488179		6.67	0.2	1.2	0.14	0.024	0.75	12.8	7.6	0.58	106	46	0.04	4.7	207	230
C488181		0.32	0.23	<0.1	<0.01	0.006	0.02	0.6	0.9	12.4	189	0.74	0.01	0.2	7.6	170
C488182		4.92	0.17	0.9	0.12	0.015	0.6	15	5.3	0.17	68	41.6	0.03	3.4	169.5	490
C488183		4.7	0.16	0.9	0.08	0.016	0.58	7.9	5.9	0.15	91	45	0.03	3.3	132	130
C488184		4.93	0.14	0.7	0.08	0.016	0.6	11.9	5.8	0.19	72	40.7	0.03	3.2	130	220
C488185		4.58	0.14	0.8	0.07	0.016	0.57	8.9	6.5	0.24	149	47.1	0.04	3.4	189	150
C488186		3.98	0.12	0.8	0.06	0.015	0.53	9.4	7.5	0.1	64	40.8	0.03	3.1	146	210
C488187		3.73	0.11	0.7	0.06	0.012	0.43	6.8	6.3	0.11	92	46.2	0.04	2.9	144.5	130
C488188		2.71	0.11	0.5	0.06	0.01	0.33	6.1	8.7	0.07	79	39.3	0.03	2.2	119.5	220
C488189		4.27	0.15	0.8	0.12	0.013	0.47	11.6	6.1	0.12	76	52.4	0.03	3.3	148.5	240
C488190		3.84	0.14	0.7	0.12	0.012	0.42	5.4	7.8	0.09	83	47.3	0.03	2.8	173.5	170
C488191		6.36	0.19	0.8	0.10	0.018	0.45	4.8	5.4	0.16	148	40.7	0.03	3.1	212	370
C488193		0.32	0.08	<0.1	<0.01	0.011	0.03	0.8	0.7	12.6	222	0.93	0.01	0.2	3.3	220
C488194		23.8	0.46	2.5	0.15	0.062	2.13	8.6	14.4	0.51	121	66.5	0.12	10.7	459	640
C488195		11.4	0.2	1.4	0.08	0.042	1.15	10.2	6.5	0.44	158	31.4	0.09	5.7	214	220
C488196		10.6	0.19	1.5	0.12	0.039	1.19	26.6	5.4	0.49	191	32.4	0.08	6	117	250
C488197		13.95	0.18	2.1	0.14	0.047	1.6	22.8	7.5	0.72	182	36.8	0.09	8.3	139.5	320
C488198		10.6	0.15	1.7	0.10	0.037	1.24	22.4	5.5	0.42	128	26.1	0.13	6.4	93.5	230
C488199		14.85	0.14	2.3	0.13	0.044	1.65	23.5	6.5	0.46	112	30.3	0.15	8.7	111.5	350
C488200		12.3	0.14	1.8	0.12	0.041	1.41	19.2	5.6	0.42	97	35.2	0.11	7	132.5	200

Comments: Interference: Ca>10% on ICP-MS As,ICP-AES results shown. REE's may not be totally soluble in MS61 method.

ALS Chemex

EXCELLENCE IN ANALYTICAL CHEMISTRY

ALS Canada Ltd.

212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: STRATEGIC METALS LTD.
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO RICH

Finalized Date: 30-SEP-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07098284

Sample Description	Method	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61
	Analyte	Pb	Rb	Re	S	Sb	Sc	Se	Sn	Sr	Ta	Te	Th	Ti	Tl	U
	Units	ppm	ppm	ppm	%	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm
	LOR	0.5	0.1	0.002	0.01	0.05	0.1	1	0.2	0.2	0.05	0.05	0.2	0.005	0.02	0.1
C488171		6.4	38.8	0.031	1.03	12.1	4.9	11	0.8	29.7	0.21	0.09	2.5	0.096	2.95	6.6
C488172		5.6	39.2	0.042	1.03	11.95	4.8	11	0.8	41.4	0.21	0.1	2.4	0.094	2.83	7.1
C488173		6.7	39.2	0.047	1.37	29.3	4.9	23	0.9	79.2	0.21	0.14	2.3	0.098	2.96	6.6
C488174		5.4	36.6	0.056	0.94	17.2	3.7	15	0.8	30.9	0.18	0.14	2.1	0.081	2.53	6.8
C488175		4.7	27.1	0.052	0.82	12.6	3.7	12	0.6	95.7	0.16	0.12	1.7	0.068	2.34	8.7
C488176		4.9	27.1	0.066	0.91	13.1	3.2	14	0.8	54.1	0.17	0.15	1.8	0.067	3.27	7.5
C488177		4.6	26	0.057	0.8	15.95	3.5	15	0.6	40.5	0.15	0.13	1.7	0.063	3.53	7.3
C488178		1.6	1.1	0.015	0.02	0.13	0.3	2	<0.2	49.9	<0.05	<0.05	<0.2	<0.005	0.02	0.7
C488179		7.6	43.6	0.058	1.78	18.25	5.5	26	1	39.2	0.26	0.28	2.4	0.122	6.9	7.2
C488181		1.5	1.2	0.008	0.02	0.15	0.4	1	0.2	46.6	<0.05	<0.05	<0.2	<0.005	0.04	0.7
C488182		6.9	35.7	0.048	1.29	11.45	4.4	19	0.6	50.9	0.2	0.22	2.3	0.094	3.53	8.5
C488183		5.4	36.3	0.05	1.05	8.57	4.1	15	0.7	30.6	0.19	0.13	2.1	0.079	2.86	7.4
C488184		5.7	38.2	0.042	0.99	6.34	4	11	0.7	45.8	0.19	0.11	2.2	0.084	2.46	7.2
C488185		5.2	34.3	0.048	0.96	5.76	4.5	12	0.8	50.5	0.18	0.11	2	0.079	2.6	8.5
C488186		4.9	31	0.053	0.9	4.3	3.7	10	0.9	45.2	0.18	0.12	2	0.073	2.33	6.9
C488187		4.8	25.7	0.041	0.85	3.27	3.5	10	2.7	47.2	0.16	0.1	1.7	0.064	2	7.6
C488188		3.9	20.2	0.033	0.73	2.41	2.7	10	0.8	60.9	0.12	0.07	1.3	0.048	1.91	6
C488189		5.6	30.8	0.037	1.13	3.88	4.1	15	0.7	65.8	0.2	0.09	1.9	0.076	3.24	7.8
C488190		5.2	26.4	0.042	1.05	4.23	3.7	16	0.8	60.6	0.17	0.09	1.8	0.068	3.44	7.7
C488191		4.9	29.9	0.045	1.05	5.5	4.3	29	0.8	135.5	0.19	0.22	1.9	0.075	4.06	9.4
C488193		1.4	1.3	<0.002	0.03	0.16	0.6	2	0.2	44.2	<0.05	0.05	<0.2	<0.005	0.05	0.7
C488194		11.8	146.5	0.129	3.48	14.95	13.2	73	2.4	147	0.69	0.27	4.9	0.311	10.1	19.3
C488195		6.1	83.9	0.056	2.01	7.81	8.1	29	1.2	294	0.35	0.09	3.2	0.173	4.41	6.8
C488196		8.8	81.6	0.037	2.1	7.59	8.9	22	1.3	230	0.37	0.07	4.5	0.18	4.24	6.5
C488197		11.8	111.5	0.036	2.65	8.76	10.6	22	1.9	109.5	0.54	0.09	6.5	0.272	5.5	6.6
C488198		8.9	83.1	0.022	2.12	5.91	8.2	10	1.5	169	0.4	0.06	5.1	0.207	3.71	4.4
C488199		11.9	116	0.022	2.66	6.72	11.1	11	1.9	106.5	0.57	0.08	7	0.292	4.5	5.2
C488200		10.4	97.6	0.031	2.4	5.18	9.8	10	1.7	92.7	0.45	0.08	5.6	0.232	4.8	5.7

Comments: Interference: Ca>10% on ICP-MS As,ICP-AES results shown. REE's may not be totally soluble in MS61 method.

ALS Chemex
EXCELLENCE IN ANALYTICAL CHEMISTRY
ALS Canada Ltd.
212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO RICH

Finalized Date: 30-SEP-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07098284

Sample Description	Method / Analyte / Units / LOR	ME-MS61 V ppm 1	ME-MS61 W ppm 0.1	ME-MS61 Y ppm 0.1	ME-MS61 Zn ppm 2	ME-MS61 Zr ppm 0.5
C488171		670	0.7	12.7	475	31.6
C488172		640	0.6	12.1	380	32.3
C488173		1045	1	22.6	1050	31.5
C488174		909	0.4	13.3	839	32.2
C488175		578	0.4	25.2	484	29.1
C488176		607	0.4	11.6	496	30.4
C488177		728	0.4	17.7	949	31.6
C488178		5	0.1	1	19	<0.5
C488179		876	0.6	16.3	794	50.7
C488181		5	0.1	0.9	17	0.6
C488182		526	0.6	16.3	324	35.4
C488183		486	0.4	20.5	245	35.8
C488184		493	0.5	16.8	285	31.7
C488185		425	0.5	35.1	446	34.7
C488186		355	0.4	13.3	203	31.4
C488187		287	0.4	15.2	213	29.5
C488188		141	1.7	8	88	24
C488189		194	0.4	10.7	128	33.3
C488190		383	0.5	14	311	30.2
C488191		529	0.4	17.8	677	38.7
C488193		7	0.1	1.1	18	0.7
C488194		944	1.2	24.4	573	93.6
C488195		538	0.6	36.2	277	47.6
C488196		607	0.7	60.7	271	50.2
C488197		829	0.9	13.6	406	69.8
C488198		567	0.7	22.1	325	55.9
C488199		705	1	20.4	322	70.6
C488200		686	0.8	15.2	285	59.8

Comments: Interference: Ca>10% on ICP-MS As,ICP-AES results shown. REE's may not be totally soluble in MS61 method.

ALS Chemex
EXCELLENCE IN ANALYTICAL CHEMISTRY
ALS Canada Ltd.
212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Finalized Date: 31-OCT-2007
Account: MTT

CERTIFICATE VA07097517

Project: NIMO - RICH

P.O. No.: R107-18

This report is for 1 Rock sample submitted to our lab in Vancouver, BC, Canada on 31-AUG-2007.

The following have access to data associated with this certificate:

AL ARCHER VANCOUVER OFFICE	DOUG EATON BILL WENGZYNOWSKI	JOAN MARIACHER

SAMPLE PREPARATION

ALS CODE	DESCRIPTION
WEI-21	Received Sample Weight
LOG-22	Sample login - Rcd w/o BarCode
CRU-31	Fine crushing - 70% <2mm
SPL-21	Split sample - riffle splitter
PUL-31	Pulverize split to 85% <75 um

ANALYTICAL PROCEDURES

ALS CODE	DESCRIPTION	
ME-MS61	48 element four acid ICP-MS	
Hg-CV41	Trace Hg - cold vapor/AAS	FIMS
ME-OG62	Ore Grade Elements - Four Acid	ICP-AES
Ni-OG62	Ore Grade Ni - Four Acid	VARIABLE
ME-MS42	Up to 34 elements by ICP-MS	ICP-MS
PGM-ICP23	Pt, Pd, Au 30g FA ICP	ICP-AES
Ni-AA62	Ore grade Ni - four acid / AA	AAS
Mo-AA62	Ore grade Mo - four acid / AA	AAS
Zn-AA62	Ore grade Zn - four acid / AAS	AAS

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

This is the Final Report and supersedes any preliminary report with this certificate number. Results apply to samples as submitted. All pages of this report have been checked and approved for release.

Signature:

Lawrence Ng, Laboratory Manager - Vancouver

ALS Chemex
EXCELLENCE IN ANALYTICAL CHEMISTRY
ALS Canada Ltd.
212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO - RICH

Finalized Date: 31-OCT-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07097517

Sample Description	Method	WEI-21	Ni-AA62	Mo-AA62	Zn-AA62	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61
	Analyte	Recvd Wt.	Ni	Mo	Zn	Ag	Al	As	Ba	Be	Bi	Ca	Cd	Ce	Co	Cr
	Units	kg	%	%	%	ppm	%	ppm	ppm	ppm	ppm	%	ppm	ppm	ppm	ppm
	LOR	0.02	0.01	0.001	0.01	0.01	0.01	0.2	10	0.05	0.01	0.01	0.02	0.01	0.1	1
C488360		0.08	4.30	0.175	0.72	2.06	5.48	1450	210	2.38	0.57	0.22	57.6	16.35	142.5	102

Comments: Interference: Mo>400ppm on ICP-MS Cd,ICP-AES results shown. Detection limits on samples requiring dilutions for Hg-CV41, due to inteferences or high concentration levels, have been increased according to dilution factor.

ALS Chemex
EXCELLENCE IN ANALYTICAL CHEMISTRY
ALS Canada Ltd.
212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO - RICH

Finalized Date: 31-OCT-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07097517

Sample Description	Method	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	Hg-CV41	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61
	Analyte	Cs	Cu	Fe	Ga	Ge	Hf	Hg	In	K	La	Li	Mg	Mn	Mo	Na
	Units	ppm	ppm	%	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	%	ppm	ppm	%
	LOR	0.05	0.2	0.01	0.05	0.05	0.1	0.1	0.005	0.01	0.5	0.2	0.01	5	0.05	0.01
C488360		8.86	193.5	11.8	23.6	5.16	1.9	0.5	0.583	1.68	6.9	10.6	0.35	130	1720	0.08

Comments: Interference: Mo>400ppm on ICP-MS Cd,ICP-AES results shown. Detection limits on samples requiring dilutions for Hg-CV41, due to inteferences or high concentration levels, have been increased according to dilution factor.

ALS Chemex
EXCELLENCE IN ANALYTICAL CHEMISTRY
ALS Canada Ltd.
212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO - RICH

Finalized Date: 31-OCT-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07097517

Sample Description	Method	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61
	Analyte	Nb	Ni	P	Pb	Rb	Re	S	Sb	Sc	Se	Sn	Sr	Ta	Te	Th
	Units	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm
	LOR	0.1	0.2	10	0.5	0.1	0.002	0.01	0.05	0.1	1	0.2	0.2	0.05	0.05	0.2
C488360		8	>10000	890	38.9	119	27.2	>10.0	70.5	11.1	>1000	8.8	61.2	0.46	15.55	3.8

Comments: Interference: Mo>400ppm on ICP-MS Cd,ICP-AES results shown. Detection limits on samples requiring dilutions for Hg-CV41, due to inteferences or high concentration levels, have been increased according to dilution factor.

ALS Chemex
EXCELLENCE IN ANALYTICAL CHEMISTRY
ALS Canada Ltd.
212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO - RICH

Finalized Date: 31-OCT-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07097517

Sample Description	Method	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	Ni-OG62	ME-MS42	PGM-ICP23	PGM-ICP23	PGM-ICP23
	Analyte	Ti	Tl	U	V	W	Y	Zn	Zr	Ni	Re	Au	Pt	Pd
	Units	%	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppm	ppm
	LOR	0.005	0.02	0.1	1	0.1	0.1	2	0.5	0.01	0.001	0.001	0.005	0.001
C488360		0.227	161	18.7	903	3.1	26.2	7420	67.2	4.44	29.6	0.079	0.194	0.125

Comments: Interference: Mo>400ppm on ICP-MS Cd,ICP-AES results shown. Detection limits on samples requiring dilutions for Hg-CV41, due to inteferences or high concentration levels, have been increased according to dilution factor.

ALS Chemex
EXCELLENCE IN ANALYTICAL CHEMISTRY
ALS Canada Ltd.
212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Finalized Date: 31-OCT-2007
Account: MTT

CERTIFICATE VA07097516

Project: NIMO - RICH

P.O. No.: R107-16

This report is for 1 Rock sample submitted to our lab in Vancouver, BC, Canada on 31-AUG-2007.

The following have access to data associated with this certificate:

AL ARCHER VANCOUVER OFFICE	DOUG EATON BILL WENGZYNOWSKI	JOAN MARIACHER

SAMPLE PREPARATION

ALS CODE	DESCRIPTION
WEI-21	Received Sample Weight
LOG-22	Sample login - Rcd w/o BarCode
CRU-31	Fine crushing - 70% <2mm
SPL-21	Split sample - riffle splitter
PUL-31	Pulverize split to 85% <75 um

ANALYTICAL PROCEDURES

ALS CODE	DESCRIPTION	
ME-MS61	48 element four acid ICP-MS	
Hg-CV41	Trace Hg - cold vapor/AAS	FIMS
ME-OG62	Ore Grade Elements - Four Acid	ICP-AES
Ni-OG62	Ore Grade Ni - Four Acid	VARIABLE
Zn-OG62	Ore Grade Zn - Four Acid	VARIABLE
ME-MS42	Up to 34 elements by ICP-MS	ICP-MS
PGM-ICP23	Pt, Pd, Au 30g FA ICP	ICP-AES
Ni-AA62	Ore grade Ni - four acid / AA	AAS
Mo-AA62	Ore grade Mo - four acid / AA	AAS
Zn-AA62	Ore grade Zn - four acid / AAS	AAS

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

is the Final Report and supersedes any preliminary report with this certificate number. Results apply to samples as submitted. All es of this report have been checked and approved for release.

Signature: Lawrence Ng

Lawrence Ng, Laboratory Manager - Vancouver

ALS Chemex
EXCELLENCE IN ANALYTICAL CHEMISTRY
ALS Canada Ltd.
212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO - RICH

Finalized Date: 31-OCT-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07097516

Sample Description	Method	WEI-21	Ni-AA62	Mo-AA62	Zn-AA62	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61
	Analyte	Recvd Wt.	Ni	Mo	Zn	Ag	Al	As	Ba	Be	Bi	Ca	Cd	Ce	Co	Cr
	Units	kg	%	%	%	ppm	%	ppm	ppm	ppm	ppm	%	ppm	ppm	ppm	ppm
	LOR	0.02	0.01	0.001	0.01	0.01	0.01	0.2	10	0.05	0.01	0.01	0.02	0.01	0.1	1
C488408		0.02	4.56	0.289	1.05	3.85	3.05	2630	160	1.53	0.74	0.36	80.2	10.85	158	62

Comments: Additional Au result for sample C488408 reports 0.097ppm Interference: Mo>400ppm on ICP-MS Cd,ICP-AES results shown. Detection limits on samples requiring dilutions for Hg-CV41, due to interferences or high concentration levels, have been increased.

ALS Chemex
EXCELLENCE IN ANALYTICAL CHEMISTRY
ALS Canada Ltd.
212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO - RICH

Finalized Date: 31-OCT-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07097516

Sample Description	Method	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	Hg-CV41	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61
	Analyte	Cs	Cu	Fe	Ga	Ge	Hf	Hg	In	K	La	Li	Mg	Mn	Mo	Na
	Units	ppm	ppm	%	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	%	ppm	ppm	%
	LOR	0.05	0.2	0.01	0.05	0.05	0.1	1	0.005	0.01	0.5	0.2	0.01	5	0.05	0.01
C488408		4.11	182.5	15.35	14.05	5.71	1	<1	0.978	0.99	5.3	10.7	0.18	112	2790	0.03

Comments: Additional Au result for sample C488408 reports 0.097ppm Interference: Mo>400ppm on ICP-MS Cd,ICP-AES results shown. Detection limits on samples requiring dilutions for Hg-CV41, due to nteferences or high concentration levels, have been increased.

ALS Chemex
EXCELLENCE IN ANALYTICAL CHEMISTRY
ALS Canada Ltd.
212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO - RICH

Finalized Date: 31-OCT-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07097516

Sample Description	Method	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61
	Analyte	Nb	Ni	P	Pb	Rb	Re	S	Sb	Sc	Se	Sn	Sr	Ta	Te	Th
	Units	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm
	LOR	0.1	0.2	10	0.5	0.1	0.002	0.01	0.05	0.1	1	0.2	0.2	0.05	0.05	0.2
C488408		4.3	>10000	1690	72.9	65.1	34.2	>10.0	91.1	6.9	>1000	13.2	94.5	0.22	20.2	2.4

Comments: Additional Au result for sample C488408 reports 0.097ppm Interference: Mo>400ppm on ICP-MS Cd,ICP-AES results shown. Detection limits on samples requiring dilutions for Hg-CV41, due to inteferences or high concentration levels, have been increased.

ALS Chemex
EXCELLENCE IN ANALYTICAL CHEMISTRY
ALS Canada Ltd.
212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO - RICH

Finalized Date: 31-OCT-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07097516

Sample Description	Method	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	Ni-OG62	Zn-OG62	ME-MS42	PGM-ICP23	PGM-ICP23	PGM-ICP23	PGM-ICP23
	Analyte	Ti	Tl	U	V	W	Y	Zn	Zr	Ni	Zn	Re	Au	Au Check	Pt	Pt Check
	Units	%	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%	%	ppm	ppm	ppm	ppm	ppm
	LOR	0.005	0.02	0.1	1	0.1	0.1	2	0.5	0.01	0.01	0.001	0.001	0.001	0.005	0.005
C488408		0.116	292	21.6	472	5.3	17.2	>10000	36.4	6.01	1.11	38.5	0.158	0.093	0.225	0.243

Comments: Additional Au result for sample C488408 reports 0.097ppm Interference: Mo>400ppm on ICP-MS Cd,ICP-AES results shown. Detection limits on samples requiring dilutions for Hg-CV41, due to nteferences or high concentration levels, have been increased.

ALS Chemex
EXCELLENCE IN ANALYTICAL CHEMISTRY
ALS Canada Ltd.
212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO - RICH

Finalized Date: 31-OCT-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07097516

Sample Description	Method	PGM-ICP23	PGM-ICP23
	Analyte	Pd	Pd Check
	Units	ppm	ppm
	LOR	0.001	0.001
C488408		0.152	0.155

Comments: Additional Au result for sample C488408 reports 0.097ppm Interference: Mo>400ppm on ICP-MS Cd,ICP-AES results shown. Detection limits on samples requiring dilutions for Hg-CV41, due to inteferences or high concentration levels, have been increased.

ALS Chemex
EXCELLENCE IN ANALYTICAL CHEMISTRY
ALS Canada Ltd.
212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Finalized Date: 30-SEP-2007
Account: MTT

CERTIFICATE VA07097257

Project: NIMO-RICH

P.O. No.: R107-10

This report is for 17 Drill Core samples submitted to our lab in Vancouver, BC, Canada on 15-AUG-2007.

The following have access to data associated with this certificate:

AL ARCHER VANCOUVER OFFICE	DOUG EATON BILL WENGZYNOWSKI	JOAN MARIACHER

SAMPLE PREPARATION

ALS CODE	DESCRIPTION
WEI-21	Received Sample Weight
BAG-01	Bulk Master for Storage
LOG-22	Sample login - Rcd w/o BarCode
CRU-31	Fine crushing - 70% <2mm
SPL-21	Split sample - riffle splitter
PUL-32	Pulverize 1000g to 85% < 75 um

ANALYTICAL PROCEDURES

ALS CODE	DESCRIPTION	
ME-MS61	48 element four acid ICP-MS	
Hg-CV41	Trace Hg - cold vapor/AAS	FIMS

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

s is the Final Report and supersedes any preliminary report with this certificate number. Results apply to samples as submitted. All es of this report have been checked and approved for release.

Signature:

Lawrence Ng, Laboratory Manager - Vancouver

ALS Chemex

EXCELLENCE IN ANALYTICAL CHEMISTRY

ALS Canada Ltd.

212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO-RICH

Finalized Date: 30-SEP-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07097257

Sample Description	Method	WEI-21	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61
	Analyte	Recvd Wt.	Ag	Al	As	Ba	Be	Bi	Ca	Cd	Ce	Co	Cr	Cs	Cu	Fe
	Units	kg	ppm	%	ppm	ppm	ppm	ppm	%	ppm	ppm	ppm	ppm	ppm	ppm	%
	LOR	0.02	0.01	0.01	0.2	10	0.05	0.01	0.01	0.02	0.01	0.1	1	0.05	0.2	0.01
C488246		2.00	0.51	1.65	20.1	360	1.26	0.08	0.31	8.21	15.1	4.7	54	2.13	51.9	1.69
C488247		2.58	0.24	1.58	10.4	600	1.21	0.07	0.15	1.96	13.45	3.8	34	2.12	29.3	1.25
C488248		1.50	0.19	1.59	10.4	520	1.09	0.08	0.06	1.47	15.75	4.2	39	1.95	30.9	1.36
C488249		1.18	0.17	1.63	11.4	430	1.25	0.08	0.08	1.89	11.7	4.1	39	1.88	30.2	1.38
C488250		1.46	0.15	2.02	14.8	440	1.34	0.08	0.07	1.19	12.7	6.8	36	1.63	33.8	1.85
C488251		0.80	0.17	1.95	17.4	430	1.3	0.09	0.1	1.34	22.4	5	35	2.11	37.9	1.6
C488252		0.76	0.2	1.82	23.8	400	1.31	0.1	0.05	1.63	13.85	6.1	37	2.16	40.7	2.01
C488253		0.92	0.22	1.42	32.2	390	0.96	0.08	0.06	3.19	11.4	6.3	35	1.69	29	1.56
C488255		1.46	0.15	0.05	<5	30	0.07	0.04	19.9	0.06	1.32	0.9	1	0.19	2.8	0.44
C488256		0.88	0.64	6.83	60.1	90	3.46	0.23	0.21	4.9	55.1	14.4	99	10.55	73	3.85
C488257		0.96	0.31	3.61	25	370	1.54	0.11	0.9	2.77	27.5	7.2	57	4.45	34.3	1.84
C488258		0.98	0.19	3.16	13	260	1.34	0.09	17.6	2	28.1	5.6	40	3.09	21.3	1.41
C488259		1.78	0.21	2.86	15	920	1.14	0.09	12.15	2.91	21.4	5.3	46	3.4	20.3	1.41
C488260		1.78	0.32	4.67	22.6	540	1.69	0.2	2.8	4.07	33.7	8.7	55	5.26	35.9	2.37
C488261		1.76	0.35	5.76	23.7	290	2.27	0.17	3.43	3.89	40.6	10.8	59	6.64	36	2.59
C488262		2.24	0.33	5.57	25.3	130	2.1	0.18	2.74	3.49	37.6	10.8	58	6.36	40.4	2.94
C488263		2.78	0.51	3.84	19.6	150	1.45	0.13	2.43	3.46	27.9	8.1	48	4.23	33.5	2.15

Comments: Interference: Ca>10% on ICP-MS As,ICP-AES results shown. REE's may not be totally soluble in MS61 method.

ALS Chemex

EXCELLENCE IN ANALYTICAL CHEMISTRY

ALS Canada Ltd.

212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO-RICH

Finalized Date: 30-SEP-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07097257

Sample Description	Method	ME-MS61	ME-MS61	ME-MS61	Hg-CV41	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61
	Analyte	Ga	Ge	Hf	Hg	In	K	La	Li	Mg	Mn	Mo	Na	Nb	Ni	P
	Units	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	%	ppm	ppm	%	ppm	ppm	ppm
	LOR	0.05	0.05	0.1	0.01	0.005	0.01	0.5	0.2	0.01	5	0.05	0.01	0.1	0.2	10
C488246		4.64	0.14	0.8	0.12	0.02	0.52	10.4	5.1	0.24	91	46.4	0.03	3.2	166.5	250
C488247		4.01	0.13	0.7	0.07	0.016	0.5	8.9	4.9	0.16	65	40.5	0.03	2.9	133.5	140
C488248		3.81	0.11	0.7	0.07	0.014	0.48	10.5	7.6	0.09	66	40.4	0.03	3	161	280
C488249		3.74	0.1	0.7	0.07	0.014	0.45	7.2	7	0.12	62	51.1	0.03	3.1	182.5	210
C488250		3.51	0.13	0.7	0.08	0.012	0.44	8.1	13.7	0.09	100	54.8	0.03	3	303	340
C488251		4.5	0.14	0.9	0.11	0.023	0.52	14.8	10.6	0.13	64	57.9	0.03	3.7	186	420
C488252		4.31	0.15	0.9	0.12	0.014	0.49	8.2	8.4	0.12	80	62.6	0.03	3.5	208	150
C488253		4.17	0.2	0.7	0.08	0.015	0.36	6.1	6.1	0.09	65	43.3	0.03	2.7	549	250
C488255		0.25	0.21	<0.1	<0.01	0.011	0.02	0.8	1.1	12.6	203	0.31	<0.01	0.2	4	160
C488256		22.8	0.4	2.4	0.22	0.092	2.2	34.9	14.1	0.57	132	83.8	0.06	10.6	347	430
C488257		10.05	0.18	1.4	0.11	0.04	1.13	16.8	8.2	0.31	93	30.8	0.05	5.7	134	290
C488258		7.59	0.15	1.2	0.07	0.021	0.9	16.7	4.8	0.45	201	19.1	0.14	5	62.3	350
C488259		7.02	0.12	1	0.09	0.026	0.89	13.2	5	0.49	159	19.55	0.08	4.3	67.9	290
C488260		12.45	0.16	1.9	0.11	0.05	1.33	20.9	6.3	0.37	133	31.1	0.1	7.3	109	230
C488261		16.05	0.17	2.4	0.12	0.048	1.65	23.6	6.9	0.6	145	31.6	0.13	9.4	112	360
C488262		15	0.15	2.1	0.13	0.043	1.59	20.9	6.5	0.54	119	38.4	0.1	8.6	135	170
C488263		9.97	0.12	1.8	0.11	0.037	1.08	16.8	4.7	0.6	140	40.9	0.08	6.3	143	240

Comments: Interference: Ca>10% on ICP-MS As,ICP-AES results shown. REE's may not be totally soluble in MS61 method.

ALS Chemex
EXCELLENCE IN ANALYTICAL CHEMISTRY
ALS Canada Ltd.
212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO-RICH

Finalized Date: 30-SEP-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07097257

Sample Description	Method	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61
	Analyte	Pb	Rb	Re	S	Sb	Sc	Se	Sn	Sr	Ta	Te	Th	Ti	Tl	U
	Units	ppm	ppm	ppm	%	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm
	LOR	0.5	0.1	0.002	0.01	0.05	0.1	1	0.2	0.2	0.05	0.05	0.2	0.005	0.02	0.1
C488246		5.7	32.4	0.056	1.24	16.1	4	16	0.7	57.7	0.18	0.15	1.9	0.077	4.1	7.5
C488247		5	32.4	0.042	0.88	6.67	3.7	10	0.7	35.9	0.16	0.11	1.9	0.071	2.26	7.3
C488248		5	30.1	0.049	0.85	4.52	3.6	10	0.7	51.3	0.16	0.1	1.9	0.067	2.25	7
C488249		5.1	28.3	0.046	0.98	3.6	3.8	11	0.7	51.7	0.18	0.12	1.8	0.066	2.51	9.2
C488250		5.3	26.6	0.047	1.08	3.37	4.2	13	0.7	31.4	0.17	0.1	1.6	0.067	2.74	9.9
C488251		6.5	33.4	0.046	1.24	4.04	4.3	18	0.8	50	0.21	0.11	2.2	0.084	3.49	8.2
C488252		6.7	31.7	0.06	1.49	5.26	4.2	20	0.8	27.9	0.2	0.14	2.1	0.08	4.85	9.5
C488253		4.1	24.3	0.195	1.06	4.27	3.4	36	0.7	43	0.15	0.32	1.8	0.062	4.55	7.1
C488255		1.6	0.9	0.002	0.02	0.06	0.4	1	<0.2	45.8	<0.05	<0.05	<0.2	<0.005	<0.02	0.5
C488256		16.7	152	0.111	3.91	15.9	13.2	76	2.4	50	0.67	0.32	7.1	0.312	10.35	14.7
C488257		8.6	71.6	0.034	1.84	6.93	6.6	23	1.3	73.6	0.38	0.08	4.1	0.171	4.04	5.3
C488258		6.9	56	0.018	1.54	4.02	5.9	15	0.9	926	0.3	0.08	3.8	0.138	2.56	3.5
C488259		6.3	54.7	0.02	1.45	4.04	5.6	12	0.9	340	0.26	0.05	3.4	0.131	2.71	3.3
C488260		9.6	89.2	0.029	2.24	6.78	9.4	15	1.9	127	0.47	0.09	5.4	0.214	4.09	4.9
C488261		11.6	111.5	0.024	2.66	6.89	11.9	15	2	126	0.6	0.09	6.7	0.265	4.43	5
C488262		11.5	106	0.031	3.09	6.56	11.7	15	1.9	94.8	0.53	0.11	6	0.247	4.96	5.4
C488263		8.1	71.2	0.041	2.14	4.83	8.3	12	1.4	121.5	0.4	0.1	4.6	0.185	4.63	6.4

Comments: Interference: Ca>10% on ICP-MS As,ICP-AES results shown. REE's may not be totally soluble in MS61 method.

ALS Chemex

EXCELLENCE IN ANALYTICAL CHEMISTRY

ALS Canada Ltd.

212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO-RICH

Finalized Date: 30-SEP-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07097257

Sample Description	Method	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61
	Analyte	V	W	Y	Zn	Zr
	Units	ppm	ppm	ppm	ppm	ppm
	LOR	1	0.1	0.1	2	0.5
C488246		667	0.4	16.3	665	35.1
C488247		449	0.3	18.2	239	30.7
C488248		319	0.3	11	201	29.4
C488249		302	0.4	16.7	226	31.1
C488250		191	0.4	16	457	30.9
C488251		201	0.4	9.7	201	34.6
C488252		334	0.5	15.8	246	35.4
C488253		477	0.3	16.2	493	29.5
C488255		4	0.1	0.9	16	<0.5
C488256		1420	1.1	24.3	712	84.7
C488257		568	0.6	8.8	305	49.4
C488258		337	0.5	21.4	156	46.6
C488259		430	0.4	11.4	239	39.1
C488260		660	0.9	14.4	417	63.6
C488261		685	1	25.4	373	75.6
C488262		737	1	18.4	323	70.1
C488263		678	0.8	15.1	314	58.7

Comments: Interference: Ca>10% on ICP-MS As,ICP-AES results shown. REE's may not be totally soluble in MS61 method.

ALS Chemex
EXCELLENCE IN ANALYTICAL CHEMISTRY
ALS Canada Ltd.
212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Finalized Date: 2-NOV-2007
Account: MTT

CERTIFICATE VA07097256

Project: NIMO RICH

P.O. No.: RI07-08

This report is for 24 Drill Core samples submitted to our lab in Vancouver, BC, Canada on 15-AUG-2007.

The following have access to data associated with this certificate:

JOAN MARIACHER

SAMPLE PREPARATION

ALS CODE	DESCRIPTION
WEI-21	Received Sample Weight
LOG-22	Sample login - Rcd w/o BarCode
CRU-31	Fine crushing - 70% <2mm
SPL-21	Split sample - riffle splitter
PUL-36	Pulverize 1.5 kg to 85% <75 um
BAG-01	Bulk Master for Storage
CRU-QC	Crushing QC Test
PUL-QC	Pulverizing QC Test

ANALYTICAL PROCEDURES

ALS CODE	DESCRIPTION	INSTRUMENT
Ni-AA62	Ore grade Ni - four acid / AA	AAS
Mo-AA62	Ore grade Mo - four acid / AA	AAS
Zn-AA62	Ore grade Zn - four acid / AAS	AAS
ME-MS42	Up to 34 elements by ICP-MS	ICP-MS
PGM-ICP23	Pt, Pd, Au 30g FA ICP	ICP-AES
ME-MS61	48 element four acid ICP-MS	
Hg-CV41	Trace Hg - cold vapor/AAS	FIMS

To: **STRATEGIC METALS LTD.**
ATTN: JOAN MARIACHER
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

This is the Final Report and supersedes any preliminary report with this certificate number. Results apply to samples as submitted. All pages of this report have been checked and approved for release.

Signature:

Lawrence Ng, Laboratory Manager - Vancouver

ALS Chemex

EXCELLENCE IN ANALYTICAL CHEMISTRY

ALS Canada Ltd.

212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Finalized Date: 2-NOV-2007
Account: MTT

Project: NIMO RICH

CERTIFICATE OF ANALYSIS VA07097256

Sample Description	Method	WEI-21	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61
	Analyte	Recvd Wt.	Ag	Al	As	Ba	Be	Bi	Ca	Cd	Ce	Co	Cr	Cs	Cu	Fe
	Units	kg	ppm	%	ppm	ppm	ppm	ppm	%	ppm	ppm	ppm	ppm	ppm	ppm	%
	LOR	0.02	0.01	0.01	0.2	10	0.05	0.01	0.01	0.02	0.01	0.1	1	0.05	0.2	0.01
C488210		0.02	1.69	1.04	1100	80	0.66	0.31	1.61	13.55	20.4	78.2	50	0.88	217	18.05
C488211		0.16	0.32	0.44	257	50	0.58	0.13	18.2	3.92	33.8	27.2	14	0.38	52.7	5.34
C488212		0.20	0.74	0.48	940	30	0.57	0.26	23	4.41	32.8	52.7	24	0.43	195.5	12.1
C488213		0.20	0.76	0.47	976	20	0.47	0.3	18.5	3.47	44.7	56.8	30	0.39	186.5	13.15
C488214		0.24	0.42	0.54	673	30	0.52	0.16	24.5	1.4	24.4	35.3	24	0.44	100	9.02
C488215		1.12	0.04	0.05	<5	70	<0.05	0.01	19.7	0.07	1.18	1.2	1	0.11	2.8	0.55
C488216		0.22	0.52	0.26	777	20	0.45	0.15	24	1.69	39.6	39.6	21	0.22	98.2	11.7
C488217		0.16	0.51	0.36	692	20	0.44	0.16	22.7	2.08	29.1	39.5	23	0.31	102	13
C488218		0.26	0.29	0.33	386	30	0.48	0.09	26.7	1.12	19.7	21	17	0.28	59.4	8.37
C488219		0.30	0.16	0.58	137	80	0.71	0.08	26.3	0.61	11.75	9.8	14	0.54	28.4	4.47
C488220		0.32	0.4	0.41	810	150	0.4	0.17	20.8	2.1	26.6	37.8	25	0.41	80.3	12.3
C488221		1.48	0.14	0.05	<5	40	0.07	0.02	20.4	0.07	1.19	1	1	0.17	1.1	0.44
C488222		0.24	0.38	0.4	791	120	0.44	0.13	23.6	1.96	26.8	33.7	23	0.4	75.9	11
C488223		0.18	0.43	0.38	998	110	0.85	0.14	25.2	1.72	27.5	29.8	16	0.35	75	9.51
C488224		0.32	0.36	0.39	699	120	0.44	0.14	23.2	1.91	29.8	32.2	16	0.41	64.5	9.29
C488225		0.32	0.34	0.29	618	100	0.46	0.1	23.4	1.4	24.9	25.9	15	0.34	51.4	8.19
C488226		0.20	0.32	0.74	582	120	0.85	0.12	23.9	1.59	34.6	30	16	0.58	44.9	7.22
C488227		1.20	0.1	0.05	<5	40	0.08	0.04	19.95	0.07	1.16	0.9	1	0.22	1.2	0.41
C488228		0.20	0.27	0.49	399	90	0.73	0.09	25.3	1.76	34.6	21	14	0.44	29.3	5.41
C488229		0.10	0.78	2.03	831	190	1.04	0.33	8.33	7.78	70.4	60.6	42	2.22	93.4	14.25
C488230		0.16	1.14	2.71	1010	210	0.69	0.44	1.8	15.35	62	87.7	55	3.02	131	18.3
C488231		0.08	0.95	5.89	1470	320	2.4	0.5	0.58	69.3	40.1	79.3	104	7.48	184	11.75
C488232		0.14	0.57	6.41	732	650	2.45	0.37	0.31	16.8	40.4	50.3	94	8.88	94.4	6.98
C488233		1.14	0.09	0.05	<5	30	0.06	0.02	20	0.1	1.31	0.9	1	0.14	1.2	0.42

Comments: Interference: Ca>10% on ICP-MS As,ICP-AES results shown. Interference: Mo>400ppm on ICP-MS Cd,ICP-AES results shown. NSS is non-sufficient sample. Detection limits on samples requiring dilutions for Hg-CV41, have been increased.

ALS Chemex

EXCELLENCE IN ANALYTICAL CHEMISTRY

ALS Canada Ltd.

212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO RICH

Finalized Date: 2-NOV-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07097256

Sample Description	Method	ME-MS61	ME-MS61	ME-MS61	Hg-CV41	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61
	Analyte	Ga	Ge	Hf	Hg	In	K	La	Li	Mg	Mn	Mo	Na	Nb	Ni	P
	Units	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	%	ppm	ppm	%	ppm	ppm	ppm
	LOR	0.05	0.05	0.1	0.01	0.005	0.01	0.5	0.2	0.01	5	0.05	0.01	0.1	0.2	10
C488210		5.71	3.8	0.5	NSS	0.118	0.24	9.5	4.5	0.23	726	766	0.36	4	>10000	1610
C488211		2.85	0.97	0.3	0.2	0.047	0.1	22.4	2.3	0.55	372	125.5	0.04	1	4440	3990
C488212		5.35	2.78	0.4	0.4	0.071	0.11	22.1	2.2	0.53	197	468	0.02	1.4	>10000	4950
C488213		6.07	2.64	0.5	0.4	0.057	0.11	30.8	2.2	0.49	158	550	0.02	2.5	>10000	5240
C488214		4.59	1.77	0.4	0.3	0.033	0.12	15.9	2	0.49	172	386	0.04	1.7	>10000	3230
C488215		0.24	0.06	<0.1	<0.1	<0.005	0.02	0.6	0.9	12.55	200	2.88	<0.01	0.2	80.2	200
C488216		2.81	2.28	0.3	0.4	0.038	0.05	28.9	1.4	0.48	151	472	0.02	2	>10000	3740
C488217		3.24	2.25	0.3	0.18	0.041	0.08	21.1	1.5	0.57	152	467	0.03	1.5	>10000	3340
C488218		2.31	1.19	0.3	0.15	0.026	0.07	14.2	1.2	0.48	152	288	0.02	2.1	8010	2250
C488219		2.53	0.52	0.3	0.10	0.016	0.13	6.5	1.9	0.4	166	118.5	0.09	1.9	2270	1350
C488220		2.67	2.24	0.3	0.16	0.042	0.11	17.7	1.6	0.52	161	398	0.02	1.5	>10000	2360
C488221		0.27	0.18	<0.1	<0.01	0.009	0.03	0.8	1.1	12.95	196	0.81	<0.01	0.3	16.9	190
C488222		2.5	2.25	0.3	0.3	0.033	0.1	17	1.9	0.49	177	434	0.03	1.7	>10000	2160
C488223		2.2	2.1	0.3	0.4	0.027	0.09	19.1	3.6	0.44	204	511	0.05	1.7	>10000	2250
C488224		2.33	2.22	0.4	0.17	0.036	0.1	22	1.8	0.41	171	377	0.03	2.1	>10000	2450
C488225		1.82	1.87	0.4	0.15	0.03	0.08	20.1	1.4	0.34	157	324	0.02	2.3	9010	2040
C488226		2.71	2.17	0.4	0.15	0.038	0.17	29.2	6.8	0.37	193	270	0.1	1.9	>10000	2780
C488227		0.26	0.18	<0.1	<0.01	0.009	0.03	0.7	1.1	12.8	191	0.73	<0.01	0.2	17	190
C488228		1.83	1.38	0.6	0.10	0.033	0.11	27.2	2.3	0.39	190	187.5	0.09	2.6	6500	2530
C488229		8.06	4.09	1.6	0.3	0.138	0.65	34.6	6.1	0.34	157	498	0.07	8.2	>10000	4590
C488230		11.8	5.36	1.8	0.4	0.226	0.81	26.4	8	0.23	90	713	0.07	10.4	>10000	5390
C488231		24.7	3.88	2.4	0.6	1.29	1.78	19.3	12.5	0.42	147	1055	0.1	9.1	>10000	1190
C488232		21.4	2.28	2.6	0.2	0.339	1.98	22.1	12.4	0.46	122	501	0.09	9.6	>10000	1010
C488233		0.26	0.18	<0.1	<0.01	0.008	0.02	0.7	1	12.95	179	1.54	<0.01	0.2	22.4	160

Comments: Interference: Ca>10% on ICP-MS As,ICP-AES results shown. Interference: Mo>400ppm on ICP-MS Cd,ICP-AES results shown. NSS is non-sufficient sample. Detection limits on samples requiring dilutions for Hg-CV41, have been increased.

ALS Chemex
EXCELLENCE IN ANALYTICAL CHEMISTRY
ALS Canada Ltd.
212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO RICH

Finalized Date: 2-NOV-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07097256

Sample Description	Method	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61
	Analyte	Pb	Rb	Re	S	Sb	Sc	Se	Sn	Sr	Ta	Te	Th	Ti	Tl	U
	Units	ppm	ppm	ppm	%	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm
	LOR	0.5	0.1	0.002	0.01	0.05	0.1	1	0.2	0.2	0.05	0.05	0.2	0.005	0.02	0.1
C488210		58.2	15.3	1.69	>10.0	88	5	>1000	2.9	89.3	0.13	5.32	1.1	0.055	225	12.1
C488211		8.9	6.5	1.9	6.38	14.65	4.2	214	0.5	1345	0.06	1.29	0.8	0.018	25.2	9.2
C488212		13.5	7.9	9.01	>10.0	40.1	2.3	590	0.6	1305	0.07	3.45	1.2	0.019	70.1	14.4
C488213		17.2	8	10.3	>10.0	39.1	2.4	585	1.4	1085	0.1	3.01	1.4	0.022	69.8	35.6
C488214		8.1	8.8	7.44	>10.0	26.1	1.7	401	0.5	1600	0.1	1.88	1.2	0.025	47.2	25.1
C488215		1.9	1	0.049	0.14	0.24	0.5	4	<0.2	56.3	<0.05	<0.05	<0.2	<0.005	0.3	0.6
C488216		8.9	3.9	10.1	>10.0	29.9	1.7	500	0.4	1710	0.06	2.31	0.9	0.012	53.8	28.6
C488217		8.6	5.7	10.8	>10.0	30.6	1.6	484	0.6	1545	0.07	2.3	1	0.017	56.6	26.4
C488218		7	5.3	5.67	>10.0	17.8	1.5	271	0.3	1510	0.06	1.19	0.6	0.015	33	26.1
C488219		3	8.6	2.05	6.1	10	1.6	103	0.3	860	0.07	0.49	0.6	0.025	16.65	20
C488220		6.4	6.7	10.4	>10.0	27.4	1.3	486	0.5	954	0.07	2.35	1.1	0.021	54.2	26
C488221		1.5	1.2	0.024	0.04	0.19	0.4	2	<0.2	49.9	<0.05	0.05	<0.2	<0.005	0.08	0.8
C488222		6.7	6.3	10.55	>10.0	29.9	1.2	504	0.4	1320	0.06	2.91	0.9	0.019	56.8	37.1
C488223		8.2	4.9	9.26	>10.0	33	1.7	486	0.7	1530	<0.05	3.01	0.7	0.014	61.5	41.1
C488224		6.4	6.4	10.75	>10.0	28.8	1.4	513	0.5	1400	0.06	3.34	0.9	0.018	52.3	24.9
C488225		5.7	5.1	9.05	>10.0	24.5	1.1	431	0.4	1480	0.06	2.88	0.7	0.015	40.6	22.4
C488226		6.4	9.3	11.95	>10.0	21.6	1.6	502	0.5	1480	0.07	3.65	1.3	0.027	32.7	20.3
C488227		1.6	1.2	0.019	0.03	0.09	0.3	2	<0.2	52.9	<0.05	0.05	<0.2	<0.005	0.07	0.6
C488228		6.1	6.8	7.56	7.55	14.5	4.3	328	0.5	1560	0.09	2.47	0.9	0.023	21.5	19.6
C488229		19.9	36.6	19.2	>10.0	42.6	7.8	899	2	538	0.33	8.65	4	0.095	59.6	44.1
C488230		29.4	52.8	30.1	>10.0	53.6	7.1	>1000	3.2	160.5	0.29	12.95	4.5	0.12	71.4	57
C488231		26.5	118.5	15.05	>10.0	58.8	12.8	960	10.6	64.2	0.56	12.5	6.2	0.276	104	30.1
C488232		17.1	127	9.13	8.48	27.9	11.4	539	4.7	59.2	0.63	6.89	7.2	0.3	60.8	16.5
C488233		1.9	1	0.026	0.03	0.15	0.4	2	<0.2	54.6	<0.05	0.07	<0.2	<0.005	0.17	0.6

Comments: Interference: Ca>10% on ICP-MS As,ICP-AES results shown. Interference: Mo>400ppm on ICP-MS Cd,ICP-AES results shown. NSS is non-sufficient sample. Detection limits on samples requiring dilutions for Hg-CV41, have been increased.

ALS Chemex
EXCELLENCE IN ANALYTICAL CHEMISTRY
ALS Canada Ltd.
212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO RICH

Finalized Date: 2-NOV-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07097256

Sample Description	Method	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	Ni-AA62	Mo-AA62	Zn-AA62	ME-MS42	PGM-ICP23	PGM-ICP23	PGM-ICP23	PGM-ICP23	PGM-ICP23	PGM-ICP23
	Analyte	V	W	Y	Zn	Zr	Ni	Mo	Zn	Re	Au	Au Check	Au Check	Pt	Pt Check	Pt Check
	Units	ppm	ppm	ppm	ppm	ppm	%	%	%	ppm	ppm	ppm	ppm	ppm	ppm	ppm
	LOR	1	0.1	0.1	2	0.5	0.01	0.001	0.01	0.001	0.001	0.001	0.001	0.005	0.005	0.005
C488210		417	0.7	87.2	6930	25.8	1.14	0.073	0.68	1.720	0.331			0.169		
C488211		155	0.3	105.5	1730	16.1	0.47	0.013	0.18	2.11	0.032			0.058		
C488212		219	0.7	74.7	1560	25.1	1.85	0.047	0.15	9.20	0.068			0.129		
C488213		233	0.9	86.8	1380	25.4	2.10	0.056	0.14	10.15	0.065	0.098	0.058	0.152	0.145	0.138
C488214		182	0.9	34.3	724	19.2	1.37	0.039	0.08	7.81	0.046			0.113		
C488215		4	0.1	1	17	0.5	0.01	<0.001	<0.01	0.007	<0.001			<0.005		
C488216		117	0.9	51.2	681	17.8	1.72	0.051	0.08	10.50	0.054			0.122		
C488217		127	1	39.4	779	15	1.66	0.048	0.08	10.25	0.046			0.114		
C488218		136	0.7	34.6	397	15.8	0.86	0.030	0.05	5.76	0.021			0.045		
C488219		100	0.6	21.1	190	17.1	0.25	0.011	0.02	2.08	0.014			0.011		
C488220		132	0.8	35.8	744	14.2	1.53	0.042	0.08	10.70	0.037			0.130		
C488221		3	0.1	1	17	<0.5	0.01	<0.001	<0.01	0.009	0.001			<0.005		
C488222		132	0.7	36.6	637	14.1	1.37	0.045	0.07	11.20	0.070			0.104		
C488223		119	0.6	41.3	512	14.3	1.06	0.053	0.05	9.03	0.075			0.088		
C488224		135	0.7	42.9	547	19.2	1.27	0.041	0.06	11.10	0.061			0.099		
C488225		162	0.6	43.2	400	19.9	1.03	0.037	0.05	9.33	0.050			0.074		
C488226		134	0.8	61.8	422	20.3	1.15	0.029	0.05	12.10	0.033			0.062		
C488227		3	0.1	0.9	16	<0.5	0.01	<0.001	<0.01	0.028	<0.001			<0.005		
C488228		142	0.5	69	351	38.9	0.73	0.020	0.04	8.10	0.015			0.046		
C488229		503	1.1	78	1300	78.3	1.89	0.051	0.13	18.95	0.041			0.119		
C488230		1015	1.2	42.9	2290	88.3	2.85	0.074	0.25	23.1	0.061	0.063		0.169	0.175	
C488231		918	1.6	23.2	10000	89	1.89	0.107	0.99	13.75	NSS			NSS		
C488232		865	1.3	23.8	2320	88.1	1.12	0.050	0.25	9.37	0.032			0.076		
C488233		4	0.2	0.9	19	<0.5	0.01	<0.001	<0.01	0.015	0.003			0.006		

Comments: Interference: Ca>10% on ICP-MS As,ICP-AES results shown. Interference: Mo>400ppm on ICP-MS Cd,ICP-AES results shown. NSS is non-sufficient sample. Detection limits on samples requiring dilutions for Hg-CV41, have been increased.

ALS Chemex
EXCELLENCE IN ANALYTICAL CHEMISTRY
ALS Canada Ltd.
212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO RICH

Finalized Date: 2-NOV-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07097256

Sample Description	Method Analyte Units LOR	PGM-ICP23 Pd ppm 0.001	PGM-ICP23 Pd Check ppm 0.001	PGM-ICP23 Pd Check ppm 0.001
C488210		0.078		
C488211		0.023		
C488212		0.056		
C488213		0.061	0.077	0.061
C488214		0.042		
C488215		<0.001		
C488216		0.048		
C488217		0.045		
C488218		0.016		
C488219		0.011		
C488220		0.049		
C488221		<0.001		
C488222		0.040		
C488223		0.037		
C488224		0.040		
C488225		0.037		
C488226		0.039		
C488227		<0.001		
C488228		0.025		
C488229		0.072		
C488230		0.105	0.108	
C488231		NSS		
C488232		0.037		
C488233		<0.001		

Comments: Interference: Ca>10% on ICP-MS As,ICP-AES results shown. Interference: Mo>400ppm on ICP-MS Cd,ICP-AES results shown. NSS is non-sufficient sample. Detection limits on samples requiring dilutions for Hg-CV41, have been increased.

ALS Chemex
EXCELLENCE IN ANALYTICAL CHEMISTRY
ALS Canada Ltd.
212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Finalized Date: 31-OCT-2007
Account: MTT

CERTIFICATE VA07096087

Project: NIMO RICH

P.O. No.: RI07-17

This report is for 1 Rock sample submitted to our lab in Vancouver, BC, Canada on 27-AUG-2007.

The following have access to data associated with this certificate:

JOAN MARIACHER

SAMPLE PREPARATION

ALS CODE	DESCRIPTION
WEI-21	Received Sample Weight
LOG-22	Sample login - Rcd w/o BarCode
CRU-31	Fine crushing - 70% <2mm
SPL-21	Split sample - riffle splitter
PUL-31	Pulverize split to 85% <75 um

ANALYTICAL PROCEDURES

ALS CODE	DESCRIPTION	INSTRUMENT
Ni-AA62	Ore grade Ni - four acid / AA	AAS
Mo-AA62	Ore grade Mo - four acid / AA	AAS
Zn-AA62	Ore grade Zn - four acid / AAS	AAS
ME-MS42	Up to 34 elements by ICP-MS	ICP-MS
PGM-ICP23	Pt, Pd, Au 30g FA ICP	ICP-AES
ME-MS61	48 element four acid ICP-MS	
Hg-CV41	Trace Hg - cold vapor/AAS	FIMS

To: **STRATEGIC METALS LTD.**
ATTN: JOAN MARIACHER
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

is the Final Report and supersedes any preliminary report with this certificate number. Results apply to samples as submitted. All es of this report have been checked and approved for release.

Signature: Lawrence Ng

Lawrence Ng, Laboratory Manager - Vancouver

ALS Chemex
EXCELLENCE IN ANALYTICAL CHEMISTRY
ALS Canada Ltd.
212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO RICH

Finalized Date: 31-OCT-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07096087

Sample Description	Method	WEI-21	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61
	Analyte	Recvd Wt.	Ag	Al	As	Ba	Be	Bi	Ca	Cd	Ce	Co	Cr	Cs	Cu	Fe
	Units	kg	ppm	%	ppm	ppm	ppm	ppm	%	ppm	ppm	ppm	ppm	ppm	ppm	%
	LOR	0.02	0.01	0.01	0.2	10	0.05	0.01	0.01	0.02	0.01	0.1	1	0.05	0.2	0.01
C488304		0.04	2.14	2.05	2650	220	0.95	0.93	1.27	109.5	24.1	231	50	2.35	278	16.55

Comments: Interference: Mo>400ppm on ICP-MS Cd,ICP-AES results shown. REE's may not be totally soluble in MS61 method. Detection limits on samples requiring dilutions for Hg-CV41, due to inteferences or high concentration levels, have been increased according to

ALS Chemex
EXCELLENCE IN ANALYTICAL CHEMISTRY
ALS Canada Ltd.
212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO RICH

Finalized Date: 31-OCT-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07096087

Sample Description	Method	ME-MS61	ME-MS61	ME-MS61	Hg-CV41	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61
	Analyte	Ga	Ge	Hf	Hg	In	K	La	Li	Mg	Mn	Mo	Na	Nb	Ni	P
	Units	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	%	ppm	ppm	%	ppm	ppm	ppm
	LOR	0.05	0.05	0.1	1	0.005	0.01	0.5	0.2	0.01	5	0.05	0.01	0.1	0.2	10
C488304		14.05	9.16	0.8	1	0.874	0.64	10.4	10.7	0.11	69	2460	0.03	2.9	>10000	6300

Comments: Interference: Mo>400ppm on ICP-MS Cd,ICP-AES results shown. REE's may not be totally soluble in MS61 method. Detection limits on samples requiring dilutions for Hg-CV41, due to inteferences or high concentration levels, have been increased according to

ALS Chemex
EXCELLENCE IN ANALYTICAL CHEMISTRY
ALS Canada Ltd.
212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO RICH

Finalized Date: 31-OCT-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07096087

Sample Description	Method	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61
	Analyte	Pb	Rb	Re	S	Sb	Sc	Se	Sn	Sr	Ta	Te	Th	Ti	Tl	U
	Units	ppm	ppm	ppm	%	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm
	LOR	0.5	0.1	0.002	0.01	0.05	0.1	1	0.2	0.2	0.05	0.05	0.2	0.005	0.02	0.1
C488304		42.1	40.4	40.8	>10.0	109	5.6	>1000	10.5	365	0.17	29.9	3.2	0.079	289	30.5

Comments: Interference: Mo>400ppm on ICP-MS Cd,ICP-AES results shown. REE's may not be totally soluble in MS61 method. Detection limits on samples requiring dilutions for Hg-CV41, due to inteferences or high concentration levels, have been increased according to

ALS Chemex
EXCELLENCE IN ANALYTICAL CHEMISTRY
ALS Canada Ltd.
212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO RICH

Finalized Date: 31-OCT-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07096087

Sample Description	Method	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	Ni-AA62	Mo-AA62	Zn-AA62	ME-MS42	PGM-ICP23	PGM-ICP23	PGM-ICP23
	Analyte	V	W	Y	Zn	Zr	Ni	Mo	Zn	Re	Au	Pt	Pd
	Units	ppm	ppm	ppm	ppm	ppm	%	%	%	ppm	ppm	ppm	ppm
	LOR	1	0.1	0.1	2	0.5	0.01	0.001	0.01	0.001	0.001	0.005	0.001
C488304		404	3.3	68.1	>10000	28.3	7.04	0.256	1.54	38.6	0.089	0.254	0.158

Comments: Interference: Mo>400ppm on ICP-MS Cd,ICP-AES results shown. REE's may not be totally solubie in MS61 method. Detection limits on samples requiring dilutions for Hg-CV41, due to inteferences or high concentration levels, have been increased according to

ALS Chemex
EXCELLENCE IN ANALYTICAL CHEMISTRY
ALS Canada Ltd.
212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Finalized Date: 31-OCT-2007
Account: MTT

CERTIFICATE VA07096086

Project: NIMO RICH

P.O. No.: RI07-15

This report is for 1 Rock sample submitted to our lab in Vancouver, BC, Canada on 27-AUG-2007.

The following have access to data associated with this certificate:

JOAN MARIACHER

SAMPLE PREPARATION

ALS CODE	DESCRIPTION
WEI-21	Received Sample Weight
LOG-22	Sample login - Rcd w/o BarCode
CRU-31	Fine crushing - 70% <2mm
SPL-21	Split sample - riffle splitter
PUL-31	Pulverize split to 85% <75 um

ANALYTICAL PROCEDURES

ALS CODE	DESCRIPTION	INSTRUMENT
Ni-AA62	Ore grade Ni - four acid / AA	AAS
Zn-AA62	Ore grade Zn - four acid / AAS	AAS
Mo-AA62	Ore grade Mo - four acid / AA	AAS
ME-MS42	Up to 34 elements by ICP-MS	ICP-MS
PGM-ICP23	Pt, Pd, Au 30g FA ICP	ICP-AES
ME-MS61	48 element four acid ICP-MS	
Hg-CV41	Trace Hg - cold vapor/AAS	FIMS

To: **STRATEGIC METALS LTD.**
ATTN: JOAN MARIACHER
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

This is the Final Report and supersedes any preliminary report with this certificate number. Results apply to samples as submitted. All pages of this report have been checked and approved for release.

Signature:

Lawrence Ng, Laboratory Manager - Vancouver

ALS Chemex
EXCELLENCE IN ANALYTICAL CHEMISTRY
ALS Canada Ltd.
212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO RICH

Finalized Date: 31-OCT-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07096086

Sample Description	Method	WEI-21	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61
	Analyte	Recvd Wt.	Ag	Al	As	Ba	Be	Bi	Ca	Cd	Ce	Co	Cr	Cs	Cu	Fe
	Units	kg	ppm	%	ppm	ppm	ppm	ppm	%	ppm	ppm	ppm	ppm	ppm	ppm	%
	LOR	0.02	0.01	0.01	0.2	10	0.05	0.01	0.01	0.02	0.01	0.1	1	0.05	0.2	0.01
C488323		0.06	1.92	0.64	5320	260	<0.05	0.32	0.27	41.5	6.28	97.1	23	0.91	186	25.3

Comments: Interference: Mo>400ppm on ICP-MS Cd,ICP-AES results shown. REE's may not be totally soluble in MS61 method.

ALS Chemex
EXCELLENCE IN ANALYTICAL CHEMISTRY
ALS Canada Ltd.
212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO RICH

Finalized Date: 31-OCT-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07096086

Sample Description	Method	ME-MS61	ME-MS61	ME-MS61	Hg-CV41	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61
	Analyte	Ga	Ge	Hf	Hg	In	K	La	Li	Mg	Mn	Mo	Na	Nb	Ni	P
	Units	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	%	ppm	ppm	%	ppm	ppm	ppm
	LOR	0.05	0.05	0.1	0.01	0.005	0.01	0.5	0.2	0.01	5	0.05	0.01	0.1	0.2	10
C488323		5.9	5.78	0.2	0.24	0.109	0.18	2.5	7.6	0.03	128	2820	0.02	0.9	>10000	1380

Comments: Interference: Mo>400ppm on ICP-MS Cd,ICP-AES results shown. REE's may not be totally soluble in MS61 method.

ALS Chemex
EXCELLENCE IN ANALYTICAL CHEMISTRY
ALS Canada Ltd.
212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO RICH

Finalized Date: 31-OCT-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07096086

Sample Description	Method	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61
	Analyte	Pb	Rb	Re	S	Sb	Sc	Se	Sn	Sr	Ta	Te	Th	Ti	Tl	U
	Units	ppm	ppm	ppm	%	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm
	LOR	0.5	0.1	0.002	0.01	0.05	0.1	1	0.2	0.2	0.05	0.05	0.2	0.005	0.02	0.1
C488323		36.5	11.6	22.8	>10.0	120	2	>1000	3.9	179	<0.05	12.4	1.1	0.021	212	7.4

Comments: Interference: Mo>400ppm on ICP-MS Cd,ICP-AES results shown. REE's may not be totally soluble in MS61 method.

ALS Chemex
EXCELLENCE IN ANALYTICAL CHEMISTRY
ALS Canada Ltd
212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO RICH

Finalized Date: 31-OCT-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07096086

Sample Description	Method	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	Ni-AA62	Zn-AA62	Mo-AA62	ME-MS42	PGM-ICP23	PGM-ICP23	PGM-ICP23
	Analyte	V	W	Y	Zn	Zr	Ni	Zn	Mo	Re	Au	Pt	Pd
	Units	ppm	ppm	ppm	ppm	ppm	%	%	%	ppm	ppm	ppm	ppm
	LOR	1	0.1	0.1	2	0.5	0.01	0.01	0.001	0.001	0.001	0.005	0.001
C488323		241	0.9	14.9	3910	7.8	2.66	0.38	0.279	17.35	0.100	0.174	0.098

Comments: Interference: Mo>400ppm on ICP-MS Cd,ICP-AES results shown. REE's may not be totally soluble in MS61 method.

ALS Chemex
EXCELLENCE IN ANALYTICAL CHEMISTRY
ALS Canada Ltd.
212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Finalized Date: 2-OCT-2007
Account: MTT

CERTIFICATE VA07090719

Project: NIMO RICH

P.O. No.: RI07-13

This report is for 5 Drill Core samples submitted to our lab in Vancouver, BC, Canada on 21-AUG-2007.

The following have access to data associated with this certificate:

AL ARCHER VANCOUVER OFFICE	DOUG EATON BILL WENGZYNOWSKI	JOAN MARIACHER

SAMPLE PREPARATION

ALS CODE	DESCRIPTION
WEI-21	Received Sample Weight
LOG-22	Sample login - Rcd w/o BarCode
CRU-31	Fine crushing - 70% <2mm
SPL-21	Split sample - riffle splitter
PUL-36	Pulverize 1.5 kg to 85% <75 um
BAG-01	Bulk Master for Storage

ANALYTICAL PROCEDURES

ALS CODE	DESCRIPTION	INSTRUMENT
Hg-CV41	Trace Hg - cold vapor/AAS	FIMS
ME-MS61	48 element four acid ICP-MS	

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

is is the Final Report and supersedes any preliminary report with this certificate number. Results apply to samples as submitted. All ges of this report have been checked and approved for release.

Signature: Lawrence Ng

Lawrence Ng, Laboratory Manager - Vancouver

ALS Chemex

EXCELLENCE IN ANALYTICAL CHEMISTRY

ALS Canada Ltd.

212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO RICH

Finalized Date: 2-OCT-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07090719

Sample Description	Method	WEI-21	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61
	Analyte	Recvd Wt.	Ag	Al	As	Ba	Be	Bi	Ca	Cd	Ce	Co	Cr	Cs	Cu	Fe
	Units	kg	ppm	%	ppm	ppm	ppm	ppm	%	ppm	ppm	ppm	ppm	ppm	ppm	%
	LOR	0.02	0.01	0.01	0.2	10	0.05	0.01	0.01	0.02	0.01	0.1	1	0.05	0.2	0.01
C488287		0.55	0.37	2.21	25.2	320	1.35	0.14	0.07	5.66	21.1	9.4	49	2.49	58.7	3.02
C488288		0.48	0.27	1.88	23.6	200	1.11	0.12	1.02	6.03	18.45	8.1	49	2.04	45.6	2.63
C488289		0.61	0.37	4.47	68.8	220	3.74	0.13	1.49	6.76	26.7	33.7	51	2.55	42.2	8.55
C488290		0.57	0.44	3.39	43	200	2.28	0.15	3.36	4.49	29.2	14.2	52	2.83	53.5	3.93
C488291		0.73	0.27	1.68	18.6	230	0.92	0.1	0.08	5.06	16.6	5.7	35	1.79	31.6	2.03

Comments: REE's may not be totally soluble in MS61 method.

ALS Chemex
EXCELLENCE IN ANALYTICAL CHEMISTRY
ALS Canada Ltd.
212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: STRATEGIC METALS LTD.
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO RICH

Finalized Date: 2-OCT-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07090719

Sample Description	Method	ME-MS61	ME-MS61	ME-MS61	Hg-CV41	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61
	Analyte	Ga	Ge	Hf	Hg	In	K	La	Li	Mg	Mn	Mo	Na	Nb	Ni	P
	Units	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	%	ppm	ppm	%	ppm	ppm	ppm
	LOR	0.05	0.05	0.1	0.01	0.005	0.01	0.5	0.2	0.01	5	0.05	0.01	0.1	0.2	10
C488287		6.48	0.11	1.1	0.35	0.031	0.67	10.5	6	0.13	72	65.1	0.03	4.2	161.5	280
C488288		5.41	0.1	0.9	0.26	0.029	0.55	9.1	5.6	0.63	143	58.1	0.03	3.6	137.5	310
C488289		7.35	0.19	1.1	0.32	0.026	0.72	13.7	8.3	0.17	732	69.9	0.03	4.8	490	1650
C488290		7.8	0.15	1.3	0.39	0.029	0.86	15.3	7.5	1.92	350	81.7	0.03	5.4	241	860
C488291		4.65	0.1	0.8	0.20	0.024	0.46	8.6	5.9	0.1	79	51	0.03	3.2	121.5	290

Comments: REE's may not be totally soluble in MS61 method.

ALS Chemex

EXCELLENCE IN ANALYTICAL CHEMISTRY

ALS Canada Ltd.

212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO RICH

Finalized Date: 2-OCT-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07090719

Sample Description	Method	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61
	Analyte	Pb	Rb	Re	S	Sb	Sc	Se	Sn	Sr	Ta	Te	Th	Ti	Tl	U
	Units	ppm	ppm	ppm	%	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm
	LOR	0.5	0.1	0.002	0.01	0.05	0.1	1	0.2	0.2	0.05	0.05	0.2	0.005	0.02	0.1
C488287		10.6	39.1	0.037	3.03	2.54	6.2	12	0.9	43.5	0.27	0.16	2.4	0.113	5.63	10.1
C488288		8.7	31.9	0.033	2.39	2.12	5.3	9	0.8	93.3	0.21	0.13	2	0.092	4.22	8.5
C488289		10.8	42.2	0.042	2.82	2.78	10.3	18	0.9	115.5	0.28	0.16	2.9	0.116	4.53	15.6
C488290		11.7	47.9	0.064	3.57	3.79	9.3	16	0.9	216	0.31	0.18	3.6	0.135	5.4	20.9
C488291		6.8	27.5	0.027	1.68	2.55	4.3	8	0.7	42.6	0.2	0.1	2.2	0.081	3.03	9.9

Comments: REE's may not be totally soluble in MS61 method.

ALS Chemex
EXCELLENCE IN ANALYTICAL CHEMISTRY
ALS Canada Ltd.
212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: STRATEGIC METALS LTD.
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO RICH

Finalized Date: 2-OCT-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07090719

Sample Description	Method	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61
	Analyte	V	W	Y	Zn	Zr
	Units	ppm	ppm	ppm	ppm	ppm
	LOR	1	0.1	0.1	2	0.5
C488287		371	0.6	15.1	239	38.1
C488288		263	0.5	13.1	225	34.1
C488289		520	0.6	72	2590	47.1
C488290		452	0.6	36	699	51.7
C488291		391	0.4	10.5	264	29.9

Comments: REE's may not be totally soluble in MS61 method.

ALS Chemex
EXCELLENCE IN ANALYTICAL CHEMISTRY
ALS Canada Ltd.
212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Finalized Date: 9-OCT-2007
Account: MTT

CERTIFICATE VA07090718

Project: NIMO RICH

P.O. No.: RI07-15

This report is for 22 Drill Core samples submitted to our lab in Vancouver, BC, Canada on 21-AUG-2007.

The following have access to data associated with this certificate:

AL ARCHER VANCOUVER OFFICE	DOUG EATON BILL WENGZYNOWSKI	JOAN MARIACHER

SAMPLE PREPARATION

ALS CODE	DESCRIPTION
WEI-21	Received Sample Weight
LOG-22	Sample login - Rcd w/o BarCode
CRU-31	Fine crushing - 70% <2mm
SPL-21	Split sample - riffle splitter
PUL-36	Pulverize 1.5 kg to 85% <75 um
BAG-01	Bulk Master for Storage

ANALYTICAL PROCEDURES

ALS CODE	DESCRIPTION	INSTRUMENT
Hg-CV41	Trace Hg - cold vapor/AAS	FIMS
ME-MS61	48 element four acid ICP-MS	

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

This is the Final Report and supersedes any preliminary report with this certificate number. Results apply to samples as submitted. All pages of this report have been checked and approved for release.

Signature:

Lawrence Ng, Laboratory Manager - Vancouver

ALS Chemex

EXCELLENCE IN ANALYTICAL CHEMISTRY

ALS Canada Ltd

212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO RICH

Finalized Date: 9-OCT-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07090718

Sample Description	Method	WEI-21	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61
	Analyte	Recvd Wt.	Ag	Al	As	Ba	Be	Bi	Ca	Cd	Ce	Co	Cr	Cs	Cu	Fe
	Units	kg	ppm	%	ppm	ppm	ppm	ppm	%	ppm	ppm	ppm	ppm	ppm	ppm	%
	LOR	0.02	0.01	0.01	0.2	10	0.05	0.01	0.01	0.02	0.01	0.1	1	0.05	0.2	0.01
C488314		2.61	0.37	1.59	24.2	570	1.09	0.07	0.08	6.76	13.1	3.9	43	2.01	40.3	1.33
C488315		2.64	0.39	1.75	28.5	410	1.38	0.08	0.07	6.19	16.35	4.3	43	2.47	43.6	1.3
C488316		1.74	0.22	1.55	19.4	460	1.1	0.07	0.04	2.35	14.55	3.6	35	2.01	27.7	1.18
C488317		0.91	0.15	1.44	17.5	870	1.02	0.07	0.04	1.36	13.7	4.5	32	1.84	31.2	1.45
C488318		0.58	0.15	1.37	16.6	130	0.9	0.07	0.04	1.67	11.15	3.4	42	1.65	28.7	1.95
C488319		0.44	0.16	1.85	23.8	150	1.3	0.1	0.05	1.82	18.3	6.4	34	2.26	37.6	1.98
C488320		0.79	0.16	1.68	26.4	140	1.13	0.08	0.04	2.11	16.05	5.1	33	2.02	34.8	1.94
C488321		0.43	0.21	1.79	22.4	230	1.19	0.1	0.04	7.09	14.6	7	39	2.22	36.1	2.08
C488322		0.56	0.18	1.5	16.3	110	0.96	0.07	0.04	7.95	11.9	4.6	44	1.79	27.4	1.87
C488324		1.24	0.11	0.05	5	20	0.08	0.02	19.8	0.08	1.22	1.1	<1	0.13	1.7	0.44
C488325		0.53	0.71	8.83	93.4	90	5.6	0.29	0.26	6.19	59.6	21.3	126	13.6	92.3	5.03
C488326		0.77	0.1	1.32	10	840	0.9	0.04	32.7	0.93	20	3.1	18	1.57	9.6	0.71
C488327		0.92	0.31	3.65	21.2	150	1.43	0.13	7.55	4	32.2	7.6	54	4.69	30.1	1.94
C488328		1.00	0.27	4.1	15.7	580	1.38	0.13	3.76	3.05	36.8	7.9	51	5.14	30.3	1.97
C488329		1.90	0.29	4.51	19.2	250	1.55	0.14	3.55	4.61	38	8	56	6.06	32	2.32
C488330		1.81	0.34	5.29	17.8	220	1.89	0.16	2.54	4.22	38.5	9.4	62	6.63	32.8	2.32
C488331		2.14	0.34	5.58	22.3	290	2.09	0.18	2.4	3.51	45	10.3	55	7.34	36.4	3.25
C488332		2.80	0.32	4.67	20.3	280	1.8	0.15	1.9	3.23	37.2	9.3	55	6.07	35	2.21
C488333		2.56	0.26	3.65	17.3	290	1.55	0.13	2.17	5.68	33.6	9.2	59	4.32	35.1	2.29
C488334		0.61	0.3	3.84	16.3	310	1.78	0.13	1.32	3.06	34.3	7.6	63	5.5	46.7	1.97
C488335		0.13	0.74	0.62	44.8	90	0.15	0.06	1.78	1.07	12.15	1.5	7	0.63	97	35
C488336		0.43	0.31	4.15	16.8	380	1.62	0.13	1.69	2.18	35	7.5	65	5.5	42.9	2.26

Comments: Interference: Ca>10% on ICP-MS As,ICP-AES results shown. REE's may not be totally soluble in MS61 method.

ALS Chemex

EXCELLENCE IN ANALYTICAL CHEMISTRY

ALS Canada Ltd.

212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO RICH

Finalized Date: 9-OCT-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07090718

Sample Description	Method	ME-MS61	ME-MS61	ME-MS61	Hg-CV41	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61
	Analyte	Ga	Ge	Hf	Hg	In	K	La	Li	Mg	Mn	Mo	Na	Nb	Ni	P
	Units	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	%	ppm	ppm	%	ppm	ppm	ppm
	LOR	0.05	0.05	0.1	0.01	0.005	0.01	0.5	0.2	0.01	5	0.05	0.01	0.1	0.2	10
C488314		4.41	0.12	0.8	0.11	0.014	0.47	9	6.6	0.1	58	49	0.03	3	135	260
C488315		4.85	0.13	0.8	0.10	0.016	0.54	11.6	5.6	0.12	52	46.2	0.03	3.2	148	200
C488316		3.82	0.1	0.7	0.06	0.013	0.45	10.1	5.8	0.1	51	35.8	0.03	2.8	124.5	150
C488317		3.64	0.1	0.7	0.06	0.013	0.4	9.7	8	0.08	69	37.4	0.03	2.7	131.5	150
C488318		3.2	0.12	0.7	0.07	0.007	0.4	6.2	8	0.08	102	44.1	0.03	2.9	133.5	130
C488319		5.1	0.14	0.9	0.10	0.01	0.52	12.2	9.2	0.12	89	58.8	0.03	3.8	172	270
C488320		4.25	0.14	0.8	0.12	0.007	0.47	9.9	7	0.11	85	59.7	0.03	3.4	165.5	230
C488321		5.27	0.16	1	0.10	0.011	0.51	7.4	11.3	0.11	98	49.4	0.03	3.7	162.5	200
C488322		4.15	0.13	0.8	0.07	0.009	0.4	6.3	11.1	0.09	97	40	0.03	3	155	190
C488324		0.27	0.13	<0.1	<0.01	0.007	0.02	0.8	1	13.05	195	0.44	0.01	0.2	2.6	170
C488325		33.3	0.57	3.3	0.27	0.09	2.96	32.9	21.2	0.77	171	112.5	0.08	14.7	611	300
C488326		3.83	0.14	0.5	0.05	0.01	0.4	14.4	2.9	0.52	193	9.37	0.03	2.1	38.2	560
C488327		9.35	0.15	1.4	0.14	0.049	1.14	20.6	6.5	0.37	162	32.9	0.06	5.7	113	210
C488328		10.15	0.17	1.6	0.13	0.038	1.18	22.5	7.4	0.34	122	29.9	0.07	6.6	104.5	310
C488329		11.15	0.16	1.7	0.14	0.05	1.31	22.3	7.7	0.49	148	32.7	0.08	6.8	115	220
C488330		13.4	0.15	2	0.14	0.047	1.48	22	8.1	0.47	123	31.6	0.12	7.9	112.5	200
C488331		14.4	0.17	2.1	0.18	0.043	1.58	24.4	8.3	0.47	119	30.9	0.11	8.4	118.5	270
C488332		11.8	0.15	1.8	0.15	0.043	1.3	21.2	7.2	0.44	106	38.2	0.08	6.9	148	200
C488333		8.98	0.14	1.7	0.13	0.032	1.01	20.1	7.7	0.45	155	43.2	0.09	5.8	190	270
C488334		9.82	0.13	1.8	0.12	0.04	1.09	21.6	6.2	0.28	82	54.1	0.11	6.4	163	350
C488335		1.67	0.75	0.3	0.16	0.021	0.18	10.1	1.5	0.06	50	8.65	0.05	1.3	38.4	630
C488336		10.6	0.13	1.9	0.12	0.039	1.2	22	6	0.31	103	53.6	0.15	7.2	156	240

Comments: Interference: Ca>10% on ICP-MS As,ICP-AES results shown. REE's may not be totally soluble in MS61 method.

ALS Chemex

EXCELLENCE IN ANALYTICAL CHEMISTRY

ALS Canada Ltd.

212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO RICH

Finalized Date: 9-OCT-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07090718

Sample Description	Method	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61
	Analyte	Pb	Rb	Re	S	Sb	Sc	Se	Sn	Sr	Ta	Te	Th	Ti	Tl	U
	Units	ppm	ppm	ppm	%	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm
	LOR	0.5	0.1	0.002	0.01	0.05	0.1	1	0.2	0.2	0.05	0.05	0.2	0.005	0.02	0.1
C488314		4.8	30.9	0.064	0.94	16.25	3.4	21	0.7	41.6	0.18	0.14	1.9	0.076	2.72	7.9
C488315		5.4	35.6	0.054	1.12	15.25	4.1	21	0.7	31	0.19	0.13	2.1	0.084	3.14	8.1
C488316		4.7	29.4	0.042	0.9	6.88	3.4	14	0.6	33.5	0.17	0.09	1.9	0.072	2.3	6.6
C488317		4.5	26.8	0.041	0.86	5.53	3.2	15	0.7	56.5	0.16	0.09	1.6	0.064	1.86	6.5
C488318		4.4	24.4	0.038	0.77	4.66	3.4	11	1	55.3	0.15	0.1	1.6	0.06	2.13	7.3
C488319		6.2	34.3	0.043	1.1	6.07	4.7	17	0.8	83.5	0.2	0.1	2.2	0.083	3.2	9.1
C488320		6.3	30.4	0.042	1.18	6.49	4.2	16	0.9	80.9	0.18	0.09	1.9	0.076	3.92	8.7
C488321		6	33.4	0.047	1.07	5.95	4.7	17	0.9	101	0.2	0.11	2.2	0.083	3.39	8.4
C488322		4	26.8	0.039	0.84	4.38	3.7	15	0.9	91.5	0.16	0.12	1.7	0.066	2.27	6.8
C488324		1.6	0.9	<0.002	0.03	<0.05	0.5	1	<0.2	53.1	<0.05	<0.05	0.2	<0.005	<0.02	1.3
C488325		21	200	0.228	4.94	23.8	15.8	95	3.3	90.8	0.89	0.39	9.1	0.415	14.35	17.9
C488326		2.8	26.7	0.007	0.79	2.6	5.4	8	0.4	643	0.11	0.06	1.5	0.056	1.31	2.9
C488327		8.7	73.2	0.033	1.92	6.58	6.3	11	1.4	282	0.37	0.08	4.3	0.169	3.52	5.5
C488328		9.2	78.8	0.028	2.08	5.3	8.3	14	1.4	170	0.43	0.08	5	0.196	3	5.7
C488329		9.4	85.8	0.031	2.29	6.79	8.7	16	1.7	172	0.43	0.1	5.2	0.208	3.77	5.7
C488330		11	98.5	0.028	2.61	6.83	9.9	14	1.7	128	0.52	0.07	5.7	0.238	3.9	5.3
C488331		13.1	105.5	0.026	3.64	7.43	10.8	16	2	96.5	0.55	0.08	6.2	0.258	4.13	5.3
C488332		9.8	91.9	0.047	2.4	5.32	9.5	16	1.6	98.4	0.45	0.1	5.1	0.217	4.62	6.2
C488333		8.4	68.2	0.058	2.1	4.64	7.6	15	1.5	120	0.37	0.12	4.6	0.18	4.2	7.7
C488334		8.4	73.3	0.058	1.83	5.52	8.4	13	1.4	101.5	0.42	0.12	4.7	0.197	3.67	8.9
C488335		24.3	12.3	0.008	>10.0	14.65	1.1	150	0.7	190.5	0.07	0.25	0.8	0.035	3.12	2.1
C488336		9	78.4	0.04	2.02	5.15	8.9	14	1.6	119.5	0.46	0.1	5.4	0.223	3.71	9.6

Comments: Interference: Ca>10% on ICP-MS As,ICP-AES results shown. REE's may not be totally soluble in MS61 method.

ALS Chemex

EXCELLENCE IN ANALYTICAL CHEMISTRY

ALS Canada Ltd.

212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO RICH

Finalized Date: 9-OCT-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07090718

Sample Description	Method / Analyte / Units / LOR	ME-MS61 V ppm 1	ME-MS61 W ppm 0.1	ME-MS61 Y ppm 0.1	ME-MS61 Zn ppm 2	ME-MS61 Zr ppm 0.5
C488314		644	0.4	13.6	628	32.2
C488315		606	0.4	16.8	520	34.1
C488316		380	0.3	12.8	238	29.5
C488317		293	0.3	12.2	180	28.7
C488318		272	0.4	15.6	189	30.9
C488319		210	0.4	14.1	162	37.8
C488320		219	0.5	15	127	34.5
C488321		533	0.4	17.7	323	38.4
C488322		456	0.3	13.4	316	32.4
C488324		5	0.1	1.1	16	<0.5
C488325		1980	1.6	34.5	1025	111
C488326		243	0.2	39.2	124	23.9
C488327		576	0.7	70.6	316	48.9
C488328		490	0.8	21.9	246	54.3
C488329		699	0.8	18.6	378	57.3
C488330		673	0.9	18	343	64.9
C488331		661	0.9	25	319	67.7
C488332		704	0.8	19.4	281	59.7
C488333		772	0.7	24.1	504	56.9
C488334		953	0.8	16	244	60.4
C488335		164	0.2	5.7	12	11.8
C488336		788	0.9	20	172	68.5

Comments: Interference: Ca>10% on ICP-MS As,ICP-AES results shown. REE's may not be totally soluble in MS61 method.

ALS Chemex
EXCELLENCE IN ANALYTICAL CHEMISTRY
ALS Canada Ltd.
212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Finalized Date: 2-OCT-2007
Account: MTT

CERTIFICATE VA07090717

Project: NIMO RICH

P.O. No.: RI07-17

This report is for 19 Drill Core samples submitted to our lab in Vancouver, BC, Canada on 21-AUG-2007.

The following have access to data associated with this certificate:

AL ARCHER VANCOUVER OFFICE	DOUG EATON BILL WENGZYNOWSKI	JOAN MARIACHER

SAMPLE PREPARATION

ALS CODE	DESCRIPTION
WEI-21	Received Sample Weight
LOG-22	Sample login - Rcd w/o BarCode
CRU-31	Fine crushing - 70% <2mm
SPL-21	Split sample - riffle splitter
PUL-36	Pulverize 1.5 kg to 85% <75 um
BAG-01	Bulk Master for Storage

ANALYTICAL PROCEDURES

ALS CODE	DESCRIPTION	INSTRUMENT
Hg-CV41	Trace Hg - cold vapor/AAS	FIMS
ME-MS61	48 element four acid ICP-MS	

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

This is the Final Report and supersedes any preliminary report with this certificate number. Results apply to samples as submitted. All pages of this report have been checked and approved for release.

Signature:

Lawrence Ng, Laboratory Manager - Vancouver

ALS Chemex

EXCELLENCE IN ANALYTICAL CHEMISTRY

ALS Canada Ltd.

212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO RICH

Finalized Date: 2-OCT-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07090717

Sample Description	Method	WEI-21	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61
	Analyte	Recvd Wt.	Ag	Al	As	Ba	Be	Bi	Ca	Cd	Ce	Co	Cr	Cs	Cu	Fe
	Units	kg	ppm	%	ppm	ppm	ppm	ppm	%	ppm	ppm	ppm	ppm	ppm	ppm	%
	LOR	0.02	0.01	0.01	0.2	10	0.05	0.01	0.01	0.02	0.01	0.1	1	0.05	0.2	0.01
C488294		2.72	0.4	1.43	14.7	220	0.93	0.07	0.14	8.11	12.65	4.1	43	1.83	48.6	1.05
C488295		2.50	0.43	2.04	20.4	200	1.53	0.09	0.06	4.2	16.15	6.1	48	2.65	44.5	1.54
C488296		1.86	0.21	1.8	14.5	160	1.35	0.09	0.05	1.78	15.75	5.7	41	2.38	31.5	1.26
C488297		1.42	0.11	0.04	<5	20	<0.05	0.16	21.1	0.07	1.26	1	<1	0.14	4.6	0.47
C488298		1.95	0.16	1.5	14.2	140	1.09	0.07	0.07	1.6	13.25	5.7	37	1.86	34.8	1.23
C488299		1.81	0.13	1.46	12.7	160	1.16	0.07	0.06	1.41	14.1	6	35	1.72	27.2	1.05
C488300		0.96	0.21	2.16	24.2	170	1.51	0.09	0.1	1.54	15.55	13.2	33	2.04	47.3	2.34
C488301		0.74	0.21	1.73	16.6	100	1.21	0.09	0.09	3.16	14.45	7.5	34	2.25	32.2	1.59
C488302		0.40	0.33	2.11	24.6	200	1.33	0.11	0.08	6.14	18.9	10.6	51	2.62	40.6	2.06
C488303		0.62	0.3	2.08	41.4	260	1.27	0.1	0.05	4.52	17.65	9.8	39	2.49	49.6	2.5
C488305		0.47	0.15	1.65	23	390	1.41	0.06	21.1	2.57	21.4	6.4	25	2.18	19.8	1.22
C488306		0.58	0.12	1.32	11	1430	0.95	0.04	22.8	0.87	10.7	2.7	15	1.4	11.6	0.79
C488307		0.89	0.19	2.21	22	1390	1.18	0.07	23.5	2.57	22.1	5.6	27	2.69	20	1.19
C488308		0.97	0.22	4.73	24	430	2.06	0.14	9.6	2.03	46	12.7	52	5.66	28.6	2.25
C488309		1.83	0.29	4.88	28.6	350	1.84	0.15	1.74	4.46	37.6	10.8	55	6.51	37.8	2.6
C488310		1.57	0.3	4.65	21.2	270	1.84	0.15	2.16	4.13	34.1	10.6	53	5.92	32.4	2.31
C488311		1.77	0.29	5.22	19.7	390	2.27	0.16	2.97	3.88	43.3	10.5	57	6.81	33.2	2.46
C488312		2.89	0.3	4.83	19.8	310	1.92	0.15	1.62	3.25	35.9	9.3	56	6.5	33.8	2.19
C488313		2.67	0.28	4.07	25	210	1.59	0.14	2.57	3.17	37.9	8.3	60	4.78	39.1	2.35

Comments: Interference: Ca>10% on ICP-MS As,ICP-AES results shown. REE's may not be totally soluble in MS61 method.

ALS Chemex

EXCELLENCE IN ANALYTICAL CHEMISTRY

ALS Canada Ltd.

212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO RICH

Finalized Date: 2-OCT-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07090717

Sample Description	Method	ME-MS61	ME-MS61	ME-MS61	Hg-CV41	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61
	Analyte	Ga	Ge	Hf	Hg	In	K	La	Li	Mg	Mn	Mo	Na	Nb	Ni	P
	Units	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	%	ppm	ppm	%	ppm	ppm	ppm
	LOR	0.05	0.05	0.1	0.01	0.005	0.01	0.5	0.2	0.01	5	0.05	0.01	0.1	0.2	10
C488294		4.1	0.12	0.7	0.09	0.017	0.43	8.5	8.5	0.15	53	46.8	0.04	2.8	127	160
C488295		5.22	0.12	0.9	0.10	0.018	0.63	9.7	14.7	0.14	54	48.7	0.04	3.7	167.5	210
C488296		4.44	0.12	0.8	0.08	0.016	0.53	10.1	16.2	0.11	50	44.1	0.04	3.3	156	190
C488297		0.23	0.11	<0.1	<0.01	0.013	0.02	0.7	0.9	13.9	200	0.3	<0.01	0.2	2.5	180
C488298		3.53	0.11	0.7	0.09	0.008	0.44	8.6	10.2	0.11	47	47.8	0.03	3	151.5	180
C488299		3.32	0.11	0.7	0.08	0.007	0.42	9.6	14.8	0.1	40	49.6	0.03	2.8	157.5	210
C488300		4.24	0.15	0.9	0.19	0.008	0.51	9.2	29.1	0.12	112	63.6	0.03	3.4	323	360
C488301		4.59	0.14	0.9	0.10	0.013	0.47	7.8	17.9	0.13	75	43.4	0.03	3.5	166	170
C488302		6.14	0.17	1.1	0.15	0.018	0.6	10	16.8	0.14	95	60.2	0.03	4.4	269	250
C488303		6.56	0.23	1	0.16	0.02	0.56	9.6	17.8	0.13	82	39.3	0.03	3.8	242	250
C488305		4.91	0.17	0.6	0.08	0.023	0.48	16	9	0.36	129	28	0.03	2.7	308	470
C488306		3.25	0.1	0.4	0.04	0.011	0.37	7	3.7	6.76	345	8.94	0.03	1.9	32.7	340
C488307		5.65	0.13	0.8	0.08	0.028	0.65	14.9	5.5	1.92	319	21.5	0.07	3.3	94.4	1030
C488308		11.45	0.17	1.7	0.12	0.03	1.43	27.9	10.2	0.66	239	25.3	0.08	6.9	149	590
C488309		12.35	0.17	1.9	0.16	0.048	1.46	22.2	11.6	0.77	188	32.2	0.08	7.4	152	250
C488310		12.05	0.14	1.7	0.13	0.041	1.38	18.8	9	0.37	117	29.2	0.07	6.9	145	140
C488311		13.75	0.16	1.9	0.15	0.045	1.57	24.9	9.9	0.45	119	29.1	0.09	7.9	119	270
C488312		12.45	0.14	1.7	0.14	0.038	1.43	20	9.1	0.45	110	34.3	0.07	6.8	130.5	190
C488313		9.92	0.13	1.8	0.13	0.034	1.19	22.5	7.3	0.32	97	41.4	0.11	6.6	153.5	280

Comments: Interference: Ca>10% on ICP-MS As,ICP-AES results shown. REE's may not be totally soluble in MS61 method.

ALS Chemex
EXCELLENCE IN ANALYTICAL CHEMISTRY
ALS Canada Ltd.
212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO RICH

Finalized Date: 2-OCT-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07090717

Sample Description	Method	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61
	Analyte	Pb	Rb	Re	S	Sb	Sc	Se	Sn	Sr	Ta	Te	Th	Ti	Tl	U
	Units	ppm	ppm	ppm	%	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm
	LOR	0.5	0.1	0.002	0.01	0.05	0.1	1	0.2	0.2	0.05	0.05	0.2	0.005	0.02	0.1
C488294		5	27	0.054	0.8	15.4	3.6	12	0.6	41.3	0.15	0.12	1.8	0.067	3.13	7.2
C488295		6.2	38.9	0.051	1.31	12.8	4.8	13	0.9	60.2	0.21	0.15	2.2	0.09	3.5	8.7
C488296		5.4	34.2	0.059	1.05	5.8	4.2	10	0.8	68.9	0.2	0.12	2.3	0.076	2.46	7.9
C488297		1.7	0.8	<0.002	0.02	0.05	0.4	1	<0.2	49.5	<0.05	<0.05	<0.2	<0.005	<0.02	0.5
C488298		5.7	27.5	0.044	1.02	4.02	3.7	10	0.6	72.2	0.16	0.09	1.7	0.068	2.32	7.9
C488299		5.2	26.1	0.039	0.95	3.36	3.6	11	0.5	87	0.16	0.09	1.7	0.066	2.39	7.9
C488300		7.4	31.6	0.05	1.91	6.09	4.7	16	0.7	96	0.2	0.12	2	0.082	4.78	12.3
C488301		5	32.4	0.044	1.08	4.39	4.5	15	0.7	84.9	0.2	0.09	2.2	0.079	2.82	8.1
C488302		6.1	39.4	0.085	1.43	6.26	6	23	0.9	148.5	0.25	0.16	2.6	0.107	4.22	10.1
C488303		6.7	37.7	0.051	2.44	7.97	5.2	62	0.7	138	0.25	0.4	2.4	0.098	4.47	8.4
C488305		3.7	32.7	0.151	1.13	4.28	3.9	33	0.7	604	0.15	0.22	1.8	0.067	3	5
C488306		2.8	24.3	0.009	0.95	2.77	2.5	12	0.4	1110	0.11	0.05	1.5	0.052	1.27	1.4
C488307		4.9	43.5	0.036	1.38	4.31	5.2	21	0.8	492	0.21	0.08	2.6	0.095	2.45	3.8
C488308		9	90	0.023	2.35	5.94	9.4	32	1.4	226	0.46	0.07	6	0.212	3.33	5.1
C488309		10.7	94.6	0.033	2.79	7.99	9	33	1.7	101	0.48	0.07	5.5	0.235	4.38	5.9
C488310		10.2	90.5	0.028	2.63	7.57	8.6	19	1.5	93.5	0.46	0.07	4.9	0.218	3.96	4.8
C488311		10.9	103	0.026	2.85	6.76	9.9	15	1.8	101.5	0.51	0.07	5.8	0.245	3.84	5
C488312		9.8	93.9	0.031	2.49	5.4	9.2	15	1.6	83.3	0.46	0.07	5.1	0.222	4.37	5.4
C488313		10.7	75.6	0.04	2.72	6.11	8.3	16	1.4	104	0.43	0.09	4.7	0.212	4.57	7.7

Comments: Interference: Ca>10% on ICP-MS As,ICP-AES results shown. REE's may not be totally soluble in MS61 method.

ALS Chemex
EXCELLENCE IN ANALYTICAL CHEMISTRY
ALS Canada Ltd.
212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: STRATEGIC METALS LTD.
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO RICH

Finalized Date: 2-OCT-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07090717

Sample Description	Method Analyte Units LOR	ME-MS61 V ppm 1	ME-MS61 W ppm 0.1	ME-MS61 Y ppm 0.1	ME-MS61 Zn ppm 2	ME-MS61 Zr ppm 0.5
C488294		621	0.4	14.1	687	31.1
C488295		559	0.5	16.1	397	37.7
C488296		367	0.4	13.1	313	32.5
C488297		4	0.3	0.9	16	<0.5
C488298		295	0.4	14.1	237	28.6
C488299		162	0.3	10.6	220	26.7
C488300		259	0.5	19.3	630	35
C488301		568	0.4	15.2	465	34.5
C488302		955	0.4	16.7	750	42.3
C488303		532	0.4	12.9	829	39.3
C488305		352	0.3	32.8	344	25.4
C488306		195	0.2	13.3	87	15.6
C488307		330	0.4	19.5	307	32
C488308		471	0.8	47.9	336	58
C488309		706	0.8	14.7	453	61.9
C488310		635	0.8	15.6	499	58.2
C488311		631	0.9	22.5	360	63.7
C488312		677	0.8	16.7	286	58.5
C488313		736	0.8	23.1	261	63.1

Comments: Interference: Ca>10% on ICP-MS As,ICP-AES results shown. REE's may not be totally soluble in MS61 method.

ALS Chemex
EXCELLENCE IN ANALYTICAL CHEMISTRY
ALS Canada Ltd.
212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Finalized Date: 2-SEP-2007
Account: MTT

CERTIFICATE VA07089981

Project: NIMO RICH

P.O. No.: RI07-10

This report is for 1 Drill Core sample submitted to our lab in Vancouver, BC, Canada on 15-AUG-2007.

The following have access to data associated with this certificate:

JOAN MARIACHER

SAMPLE PREPARATION

ALS CODE	DESCRIPTION
WEI-21	Received Sample Weight
LOG-22	Sample login - Rcd w/o BarCode
CRU-31	Fine crushing - 70% <2mm
SPL-21	Split sample - riffle splitter
PUL-31	Pulverize split to 85% <75 um

ANALYTICAL PROCEDURES

ALS CODE	DESCRIPTION	INSTRUMENT
ME-MS42	Up to 34 elements by ICP-MS	ICP-MS
PGM-ICP23	Pt, Pd, Au 30g FA ICP	ICP-AES
Ni-AA62	Ore grade Ni - four acid / AA	AAS
Zn-AA62	Ore grade Zn - four acid / AAS	AAS
Mo-AA62	Ore grade Mo - four acid / AA	AAS

To: **STRATEGIC METALS LTD.**
ATTN: JOAN MARIACHER
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

his is the Final Report and supersedes any preliminary report with this certificate number. Results apply to samples as submitted. All ages of this report have been checked and approved for release.

Signature:

Lawrence Ng, Laboratory Manager - Vancouver

ALS Chemex
EXCELLENCE IN ANALYTICAL CHEMISTRY
ALS Canada Ltd.
212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO RICH

Finalized Date: 2-SEP-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07089981

Sample Description	Method	WEI-21	Ni-AA62	Zn-AA62	Mo-AA62	ME-MS42	PGM-ICP23	PGM-ICP23	PGM-ICP23
	Analyte	Recvd Wt.	Ni	Zn	Mo	Re	Au	Pt	Pd
	Units	kg	%	%	%	ppm	ppm	ppm	ppm
	LOR	0.02	0.01	0.01	0.001	0.001	0.001	0.005	0.001
C488254		0.12	2.64	0.59	0.135	8.80	0.245	0.148	0.109

ALS Chemex
EXCELLENCE IN ANALYTICAL CHEMISTRY
ALS Canada Ltd.
212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Finalized Date: 4-SEP-2007
Account: MTT

CERTIFICATE VA07089980

Project: NIMO RICH

P.O. No.: RI07-12

This report is for 2 Drill Core samples submitted to our lab in Vancouver, BC, Canada on 15-AUG-2007.

The following have access to data associated with this certificate:

JOAN MARIACHER

SAMPLE PREPARATION

ALS CODE	DESCRIPTION
WEI-21	Received Sample Weight
LOG-22	Sample login - Rcd w/o BarCode
CRU-31	Fine crushing - 70% <2mm
SPL-21	Split sample - riffle splitter
PUL-31	Pulverize split to 85% <75 um

ANALYTICAL PROCEDURES

ALS CODE	DESCRIPTION	INSTRUMENT
ME-MS42	Up to 34 elements by ICP-MS	ICP-MS
PGM-ICP23	Pt, Pd, Au 30g FA ICP	ICP-AES
Ni-AA62	Ore grade Ni - four acid / AA	AAS
Zn-AA62	Ore grade Zn - four acid / AAS	AAS
Mo-AA62	Ore grade Mo - four acid / AA	AAS

To: **STRATEGIC METALS LTD.**
ATTN: JOAN MARIACHER
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

s is the Final Report and supersedes any preliminary report with this certificate number. Results apply to samples as submitted. All ges of this report have been checked and approved for release.

Signature:

Lawrence Ng, Laboratory Manager - Vancouver

ALS Chemex

EXCELLENCE IN ANALYTICAL CHEMISTRY

ALS Canada Ltd.

212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO RICH

Finalized Date: 4-SEP-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07089980

Sample Description	Method	WEI-21	Ni-AA62	Zn-AA62	Mo-AA62	ME-MS42	PGM-ICP23	PGM-ICP23	PGM-ICP23
	Analyte	Recvd Wt.	Ni	Zn	Mo	Re	Au	Pt	Pd
	Units	kg	%	%	%	ppm	ppm	ppm	ppm
	LOR	0.02	0.01	0.01	0.001	0.001	0.001	0.005	0.001
C488273		0.10	1.78	0.98	0.093	12.35	0.071	0.075	0.075
C488292		0.06	3.04	0.32	0.127	15.95	0.101	0.186	0.102

ALS Chemex
EXCELLENCE IN ANALYTICAL CHEMISTRY
ALS Canada Ltd.
212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Finalized Date: 13-SEP-2007
Account: MTT

CERTIFICATE VA07089919

Project: NIMO RICH

P.O. No.: RI07-06

This report is for 2 Drill Core samples submitted to our lab in Vancouver, BC, Canada on 15-AUG-2007.

The following have access to data associated with this certificate:

JOAN MARIACHER

SAMPLE PREPARATION

ALS CODE	DESCRIPTION
WEI-21	Received Sample Weight
LOG-22	Sample login - Rcd w/o BarCode
CRU-31	Fine crushing - 70% <2mm
SPL-21	Split sample - riffle splitter
PUL-31	Pulverize split to 85% <75 um

ANALYTICAL PROCEDURES

ALS CODE	DESCRIPTION	INSTRUMENT
PGM-ICP23	Pt, Pd, Au 30g FA ICP	ICP-AES
ME-MS42	Up to 34 elements by ICP-MS	ICP-MS
Ni-AA62	Ore grade Ni - four acid / AA	AAS
Zn-AA62	Ore grade Zn - four acid / AAS	AAS
Mo-AA62	Ore grade Mo - four acid / AA	AAS

To: **STRATEGIC METALS LTD.**
ATTN: JOAN MARIACHER
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

s is the Final Report and supersedes any preliminary report with this certificate number. Results apply to samples as submitted. All ges of this report have been checked and approved for release.

Signature:

Lawrence Ng, Laboratory Manager - Vancouver

ALS Chemex
EXCELLENCE IN ANALYTICAL CHEMISTRY
ALS Canada Ltd.
212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO RICH

Finalized Date: 13-SEP-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07089919

Sample Description	Method	WEI-21	Ni-AA62	Zn-AA62	Mo-AA62	PGM-ICP23	PGM-ICP23	PGM-ICP23	ME-MS42
	Analyte	Recvd Wt.	Ni	Zn	Mo	Au	Pt	Pd	Re
	Units	kg	%	%	%	ppm	ppm	ppm	ppm
	LOR	0.02	0.01	0.01	0.001	0.001	0.005	0.001	0.001
C488180		0.02	3.30	0.38	0.100	0.234	0.315	0.412	10.10
C488192		0.08	3.91	2.36	0.125	0.096	0.196	0.142	13.00

ALS Chemex
EXCELLENCE IN ANALYTICAL CHEMISTRY
ALS Canada Ltd.
212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Finalized Date: 31-OCT-2007
Account: MTT

CERTIFICATE VA07087488

Project: NIMO RICH

P.O. No.: RI07-05

This report is for 1 Drill Core sample submitted to our lab in Vancouver, BC, Canada on 10-AUG-2007.

The following have access to data associated with this certificate:

AL ARCHER VANCOUVER OFFICE	DOUG EATON BILL WENGZYNOWSKI	JOAN MARIACHER

SAMPLE PREPARATION

ALS CODE	DESCRIPTION
WEI-21	Received Sample Weight
LOG-22	Sample login - Rcd w/o BarCode
CRU-31	Fine crushing - 70% <2mm
SPL-21	Split sample - riffle splitter
PUL-36	Pulverize 1.5 kg to 85% <75 um

ANALYTICAL PROCEDURES

ALS CODE	DESCRIPTION	INSTRUMENT
Ni-AA62	Ore grade Ni - four acid / AA	AAS
ME-MS42	Up to 34 elements by ICP-MS	ICP-MS
PGM-ICP23	Pt, Pd, Au 30g FA ICP	ICP-AES
Mo-AA62	Ore grade Mo - four acid / AA	AAS
Zn-AA62	Ore grade Zn - four acid / AAS	AAS
ME-MS61	48 element four acid ICP-MS	
Hg-CV41	Trace Hg - cold vapor/AAS	FIMS

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

s is the Final Report and supersedes any preliminary report with this certificate number. Results apply to samples as submitted. All es of this report have been checked and approved for release.

Signature: Lawrence Ng

Lawrence Ng, Laboratory Manager - Vancouver

ALS Chemex
EXCELLENCE IN ANALYTICAL CHEMISTRY
ALS Canada Ltd.
212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO RICH

Finalized Date: 31-OCT-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07087488

Sample Description	Method	WEI-21	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61
	Analyte	Recvd Wt.	Ag	Al	As	Ba	Be	Bi	Ca	Cd	Ce	Co	Cr	Cs	Cu	Fe
	Units	kg	ppm	%	ppm	ppm	ppm	ppm	%	ppm	ppm	ppm	ppm	ppm	ppm	%
	LOR	0.02	0.01	0.01	0.2	10	0.05	0.01	0.01	0.02	0.01	0.1	1	0.05	0.2	0.01
C385574		0.04	1.86	3.44	998	1050	1.44	0.94	0.58	172.5	21.4	131	88	4.2	313	11.15

Comments: Interference: Mo>400ppm on ICP-MS Cd,ICP-AES results shown. Detection limits on samples requiring dilutions for Hg-CV41, due to inteferences or high concentration levels, have been increased according to dilution factor.

ALS Chemex
EXCELLENCE IN ANALYTICAL CHEMISTRY
ALS Canada Ltd.
212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO RICH

Finalized Date: 31-OCT-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07087488

Sample Description	Method	ME-MS61	ME-MS61	ME-MS61	Hg-CV41	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61
	Analyte	Ga	Ge	Hf	Hg	In	K	La	Li	Mg	Mn	Mo	Na	Nb	Ni	P
	Units	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	%	ppm	ppm	%	ppm	ppm	ppm
	LOR	0.05	0.05	0.1	0.1	0.005	0.01	0.5	0.2	0.01	5	0.05	0.01	0.1	0.2	10
C385574		30.4	5.89	1.2	1.7	1.075	1.14	12.1	13.5	0.26	57	714	0.05	5.3	>10000	2440

Comments: Interference: Mo>400ppm on ICP-MS Cd,ICP-AES results shown. Detection limits on samples requiring dilutions for Hg-CV41, due to inteferences or high concentration levels, have been increased according to dilution factor.

ALS Chemex
EXCELLENCE IN ANALYTICAL CHEMISTRY
ALS Canada Ltd.
212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO RICH

Finalized Date: 31-OCT-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07087488

Sample Description	Method	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61
	Analyte	Pb	Rb	Re	S	Sb	Sc	Se	Sn	Sr	Ta	Te	Th	Ti	Tl	U
	Units	ppm	ppm	ppm	%	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm
	LOR	0.5	0.1	0.002	0.01	0.05	0.1	1	0.2	0.2	0.05	0.05	0.2	0.005	0.02	0.1
C385574		33.9	68.8	8.4	>10.0	99.9	7.1	>1000	9.4	88.4	0.34	13.6	6.4	0.167	59.4	106.5

Comments: Interference: Mo>400ppm on ICP-MS Cd,ICP-AES results shown. Detection limits on samples requiring dilutions for Hg-CV41, due to inteferences or high concentration levels, have been increased according to dilution factor.

ALS Chemex
EXCELLENCE IN ANALYTICAL CHEMISTRY
ALS Canada Ltd.
212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO RICH

Finalized Date: 31-OCT-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07087488

Sample Description	Method	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	Ni-AA62	ME-MS42	PGM-ICP23	PGM-ICP23	PGM-ICP23	Mo-AA62	Zn-AA62
	Analyte	V	W	Y	Zn	Zr	Ni	Re	Au	Pt	Pd	Mo	Zn
	Units	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppm	ppm	%	%
	LOR	1	0.1	0.1	2	0.5	0.01	0.001	0.001	0.005	0.001	0.001	0.01
C385574		757	1.4	85.4	>10000	62.5	3.90	9.35	0.070	0.184	0.156	0.076	4.25

Comments: Interference: Mo>400ppm on ICP-MS Cd,ICP-AES results shown. Detection limits on samples requiring dilutions for Hg-CV41, due to inteferences or high concentration levels, have been increased according to dilution factor.

ALS Chemex
EXCELLENCE IN ANALYTICAL CHEMISTRY
ALS Canada Ltd.
212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Finalized Date: 13-SEP-2007
Account: MTT

CERTIFICATE VA07087487

Project: NIMO RICH

P.O. No.: RI07-074

This report is for 2 Drill Core samples submitted to our lab in Vancouver, BC, Canada on 10-AUG-2007.

The following have access to data associated with this certificate:

JOAN MARIACHER

SAMPLE PREPARATION

ALS CODE	DESCRIPTION
WEI-21	Received Sample Weight
LOG-22	Sample login - Rcd w/o BarCode
CRU-31	Fine crushing - 70% <2mm
SPL-21	Split sample - riffle splitter
PUL-31	Pulverize split to 85% <75 um

ANALYTICAL PROCEDURES

ALS CODE	DESCRIPTION	INSTRUMENT
ME-MS42	Up to 34 elements by ICP-MS	ICP-MS
PGM-ICP23	Pt, Pd, Au 30g FA ICP	ICP-AES
Ni-AA62	Ore grade Ni - four acid / AA	AAS
Zn-AA62	Ore grade Zn - four acid / AAS	AAS
Mo-AA62	Ore grade Mo - four acid / AA	AAS

To: **STRATEGIC METALS LTD.**
ATTN: JOAN MARIACHER
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

his is the Final Report and supersedes any preliminary report with this certificate number. Results apply to samples as submitted. All ages of this report have been checked and approved for release.

Signature:

Lawrence Ng, Laboratory Manager - Vancouver

ALS Chemex
EXCELLENCE IN ANALYTICAL CHEMISTRY
ALS Canada Ltd.
212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO RICH

Finalized Date: 13-SEP-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07087487

Sample Description	Method	WEI-21	Ni-AA62	Zn-AA62	Mo-AA62	ME-MS42	PGM-ICP23	PGM-ICP23	PGM-ICP23
	Analyte	Recvd Wt.	Ni	Zn	Mo	Re	Au	Pt	Pd
	Units	kg	%	%	%	ppm	ppm	ppm	ppm
	LOR	0.02	0.01	0.01	0.001	0.001	0.001	0.005	0.001
C385592		0.02	0.15	0.16	0.036	1.635	0.038	<0.005	0.056
C488158		0.08	3.60	0.46	0.250	29.6	0.097	0.207	0.128

ALS Chemex
EXCELLENCE IN ANALYTICAL CHEMISTRY
ALS Canada Ltd.
212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Finalized Date: 2-OCT-2007
Account: MTT

CERTIFICATE VA07087267

Project: NIMO RI

P.O. No.: RI07-05

This report is for 16 Drill Core samples submitted to our lab in Vancouver, BC, Canada on 8-AUG-2007.

The following have access to data associated with this certificate:

AL ARCHER VANCOUVER OFFICE	DOUG EATON BILL WENGZYNOWSKI	JOAN MARIACHER

SAMPLE PREPARATION

ALS CODE	DESCRIPTION
WEI-21	Received Sample Weight
BAG-01	Bulk Master for Storage
LOG-22	Sample login - Rcd w/o BarCode
CRU-31	Fine crushing - 70% <2mm
SPL-21	Split sample - riffle splitter
PUL-32	Pulverize 1000g to 85% < 75 um

ANALYTICAL PROCEDURES

ALS CODE	DESCRIPTION	
ME-MS61	48 element four acid ICP-MS	
Hg-CV41	Trace Hg - cold vapor/AAS	FIMS

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

is is the Final Report and supersedes any preliminary report with this certificate number. Results apply to samples as submitted. All ges of this report have been checked and approved for release.

Signature:

Lawrence Ng, Laboratory Manager - Vancouver

ALS Chemex

EXCELLENCE IN ANALYTICAL CHEMISTRY

ALS Canada Ltd.

212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO RI

Finalized Date: 2-OCT-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07087267

Sample Description	Method	WEI-21	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61
	Analyte	Recvd Wt.	Ag	Al	As	Ba	Be	Bi	Ca	Cd	Ce	Co	Cr	Cs	Cu	Fe
	Units	kg	ppm	%	ppm	ppm	ppm	ppm	%	ppm	ppm	ppm	ppm	ppm	ppm	%
	LOR	0.02	0.01	0.01	0.2	10	0.05	0.01	0.01	0.02	0.01	0.1	1	0.05	0.2	0.01
C385566		2.58	0.67	2.05	15.5	390	1.00	0.07	0.11	10.75	15.25	4.1	41	2.48	48.1	1.31
C385567		2.76	0.52	1.60	17.7	390	0.88	0.06	0.20	7.11	13.75	3.2	40	1.85	40.1	1.31
C385568		2.72	0.61	1.74	24.1	160	0.98	0.1	0.13	11.5	16.7	4.3	58	2.11	68	1.48
C385569		1.78	0.38	1.83	18.1	220	1.06	0.09	0.23	2.57	15.75	4.3	43	2.33	38.9	1.44
C385570		1.50	0.24	1.77	14.2	290	1.05	0.08	0.26	1.8	16.45	4.4	39	2.34	35.8	1.41
C385571		0.60	0.2	1.75	14.7	230	1.12	0.08	0.17	1.55	17.5	4.1	35	2.17	32.2	1.46
C385572		1.02	0.35	3.6	32.6	230	1.61	0.13	0.44	2.68	26.5	7.6	58	5.18	47.3	2.42
C385573		0.68	0.57	6.8	78.2	100	3.04	0.24	0.26	4.36	53.6	14.6	103	10.75	67.5	3.6
C385575		0.48	0.3	2.36	27	230	1.09	0.1	0.06	2	19	5.4	44	3.14	39.2	1.68
C385576		0.98	0.23	1.66	19.8	160	1.03	0.09	0.04	2.16	11.95	4.5	38	2.01	34.3	1.54
C385577		0.92	0.18	1.73	19.8	120	1.17	0.09	0.12	0.82	19.1	5.2	31	2.1	37.3	1.88
C385578		1.64	0.15	1.66	14.3	160	1.16	0.08	0.21	1.11	15.05	4.1	36	1.81	30.6	1.35
C385579		2.00	0.29	3.8	26.8	140	1.36	0.13	5.78	3.44	38.3	7.4	56	4.3	30.8	2
C385580		3.00	0.33	5.2	24.8	180	1.72	0.15	4.41	4.08	40.9	9.9	58	5.79	33.9	2.28
C385581		2.70	0.31	5.32	22.7	110	1.98	0.18	2.7	3.12	44.6	10.7	52	6.42	37	2.27
C385582		2.82	0.29	4.27	21.6	190	1.39	0.14	2.23	3.23	33.1	8.4	52	4.81	31.1	2.16

Comments: REE's may not be totally soluble in MS61 method.

ALS Chemex

EXCELLENCE IN ANALYTICAL CHEMISTRY

ALS Canada Ltd.

212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO RI

Finalized Date: 2-OCT-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07087267

Sample Description	Method	ME-MS61	ME-MS61	ME-MS61	Hg-CV41	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61
	Analyte	Ga	Ge	Hf	Hg	In	K	La	Li	Mg	Mn	Mo	Na	Nb	Ni	P
	Units	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	%	ppm	ppm	%	ppm	ppm	ppm
	LOR	0.05	0.05	0.1	0.01	0.005	0.01	0.5	0.2	0.01	5	0.05	0.01	0.1	0.2	10
C385566		6.03	0.12	0.7	0.10	0.014	0.70	10.6	7.7	0.15	77	40.30	0.04	3.4	121.0	210
C385567		4.75	0.12	0.6	0.09	0.010	0.53	10.3	8.6	0.13	79	44.20	0.03	3.0	127.0	310
C385568		5.65	0.13	1	0.15	0.024	0.59	11.7	7.4	0.12	76	60.3	0.04	4	179	230
C385569		4.98	0.11	0.9	0.10	0.016	0.64	10.4	7.4	0.15	88	49.3	0.03	3.8	155	170
C385570		4.83	0.1	0.9	0.10	0.017	0.63	10.8	7.5	0.19	93	49.7	0.04	3.7	158	150
C385571		4.62	0.1	0.9	0.08	0.017	0.56	11.4	8.7	0.16	94	46.2	0.04	3.6	172.5	240
C385572		10.8	0.17	1.5	0.16	0.046	1.16	15.8	8.8	0.31	122	49.3	0.04	6.3	156	130
C385573		24.7	0.38	2.8	0.21	0.092	2.28	29.6	13.1	0.54	108	81.8	0.07	11.8	413	850
C385575		9.1	0.22	1.1	0.10	0.02	0.72	11.3	7.6	0.18	86	46.2	0.04	4.4	197.5	170
C385576		4.37	0.12	0.8	0.11	0.014	0.48	6.2	7.2	0.12	88	54.5	0.04	3.4	151.5	100
C385577		4.39	0.13	0.8	0.11	0.01	0.5	11.7	6.6	0.13	103	56.2	0.04	3.6	166.5	250
C385578		3.83	0.12	0.7	0.06	0.013	0.47	9.7	10.2	0.11	77	60.6	0.04	3.4	190	250
C385579		9.79	0.21	1.4	0.10	0.038	1.15	24.3	7.4	0.46	159	35.3	0.07	6	113.5	340
C385580		14.2	0.2	1.9	0.13	0.044	1.6	23	6.9	0.58	133	31.8	0.13	8.2	108	240
C385581		14.8	0.2	2	0.12	0.044	1.64	24.6	7.6	0.46	101	36.4	0.14	8.6	122.5	300
C385582		10.75	0.17	1.6	0.13	0.037	1.24	18.9	6.2	0.47	107	38.5	0.11	6.5	133	220

Comments: REE's may not be totally soluble in MS61 method.

ALS Chemex

EXCELLENCE IN ANALYTICAL CHEMISTRY

ALS Canada Ltd.

212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO RI

Finalized Date: 2-OCT-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07087267

Sample Description	Method	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61
	Analyte	Pb	Rb	Re	S	Sb	Sc	Se	Sn	Sr	Ta	Te	Th	Ti	Tl	U
	Units	ppm	ppm	ppm	%	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm
	LOR	0.5	0.1	0.002	0.01	0.05	0.1	1	0.2	0.2	0.05	0.05	0.2	0.005	0.02	0.1
C385566		6.0	45.0	0.042	1.06	20.80	4.5	15	0.8	43.0	0.21	0.14	2.6	0.097	2.92	7.2
C385567		5.0	33.8	0.051	1.08	18.00	3.7	14	0.6	40.0	0.19	0.14	2.1	0.081	2.73	7.7
C385568		6.7	36.4	0.074	1.12	19.3	4.9	20	0.7	36.9	0.23	0.18	2.6	0.087	5.2	10.3
C385569		6.3	39.7	0.056	1.02	10.2	5.1	14	0.7	48.1	0.22	0.14	2.5	0.086	3.2	9.3
C385570		6	37.5	0.05	1.03	6.61	5.1	12	0.7	42.9	0.21	0.12	2.5	0.086	2.87	9.7
C385571		6.1	35.4	0.073	0.97	5.04	4.2	12	0.6	44.5	0.22	0.13	2.5	0.078	2.73	8.6
C385572		11	78.2	0.049	2	9.51	7.5	26	1.4	44	0.38	0.1	4.5	0.157	4.77	9.2
C385573		16.2	154.5	0.125	3.51	17.8	14.6	73	2.4	159.5	0.75	0.25	7.7	0.31	10.5	17.7
C385575		5.9	47.5	0.054	1.37	6.44	5.5	35	0.7	51.9	0.26	0.24	2.7	0.117	5.23	12.4
C385576		5.6	30.4	0.05	1.14	4.86	4.4	17	0.6	38.7	0.19	0.1	2	0.083	3.77	8.9
C385577		6	32.1	0.044	1.36	4.34	4.3	16	0.6	35.7	0.21	0.1	2.1	0.084	3.59	9.7
C385578		4.9	28.7	0.052	1.13	3.39	4	13	0.6	44.5	0.19	0.1	1.9	0.077	2.75	10.3
C385579		7.4	72.1	0.036	1.93	6.97	7.5	21	1.3	166.5	0.37	0.07	4.2	0.179	4.01	6.2
C385580		10.3	101.5	0.027	2.42	7.19	10	18	1.8	145	0.52	0.08	5.9	0.243	4.51	5.1
C385581		10.5	107.5	0.03	2.39	5.97	10.9	14	1.9	110.5	0.54	0.08	6.3	0.249	4.6	6
C385582		8.5	79.4	0.037	2.21	5.23	8.3	13	1.5	106	0.42	0.09	4.8	0.201	4.9	6.1

Comments: REE's may not be totally soluble in MS61 method.

ALS Chemex

EXCELLENCE IN ANALYTICAL CHEMISTRY

ALS Canada Ltd.

212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO RI

Finalized Date: 2-OCT-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07087267

Sample Description	Method	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61
	Analyte	V	W	Y	Zn	Zr
	Units	ppm	ppm	ppm	ppm	ppm
	LOR	1	0.1	0.1	2	0.5
C385566		1050	0.6	13.8	895	33.8
C385567		778	0.5	14.3	667	31.4
C385568		921	0.5	18.5	893	42.9
C385569		571	0.5	19.4	261	38.3
C385570		510	0.4	22.3	252	36.8
C385571		391	0.4	12.6	206	33.8
C385572		693	0.7	17.3	317	53.3
C385573		1480	1.2	25.3	591	95.5
C385575		710	0.5	12.7	431	42.1
C385576		486	0.4	14.2	302	32.7
C385577		207	0.4	14.6	234	31.8
C385578		232	0.4	13.6	200	31.3
C385579		628	0.7	44	325	50.6
C385580		685	0.9	25.9	336	65.3
C385581		679	1	24.4	244	69.9
C385582		686	0.8	14.1	266	57.8

Comments: REE's may not be totally soluble in MS61 method.

ALS Chemex
EXCELLENCE IN ANALYTICAL CHEMISTRY
ALS Canada Ltd.
212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Finalized Date: 25-SEP-2007
Account: MTT

CERTIFICATE VA07087265

Project: NIMO-RICH

P.O. No.: RI07-7A

This report is for 30 Drill Core samples submitted to our lab in Vancouver, BC, Canada on 8-AUG-2007.

The following have access to data associated with this certificate:

AL ARCHER VANCOUVER OFFICE	DOUG EATON BILL WENGZYNOWSKI	JOAN MARIACHER

SAMPLE PREPARATION

ALS CODE	DESCRIPTION
WEI-21	Received Sample Weight
LOG-22	Sample login - Rcd w/o BarCode
BAG-01	Bulk Master for Storage
CRU-31	Fine crushing - 70% <2mm
SPL-21	Split sample - riffle splitter
PUL-32	Pulverize 1000g to 85% < 75 um

ANALYTICAL PROCEDURES

ALS CODE	DESCRIPTION	
ME-MS61	48 element four acid ICP-MS	
Hg-CV41	Trace Hg - cold vapor/AAS	FIMS

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

is is the Final Report and supersedes any preliminary report with this certificate number. Results apply to samples as submitted. All ges of this report have been checked and approved for release.

Signature:

Lawrence Ng, Laboratory Manager - Vancouver

ALS Chemex

EXCELLENCE IN ANALYTICAL CHEMISTRY

ALS Canada Ltd.

212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO-RICH

Finalized Date: 25-SEP-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07087265

Sample Description	Method	WEI-21	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61
	Analyte	Recvd Wt.	Ag	Al	As	Ba	Be	Bi	Ca	Cd	Ce	Co	Cr	Cs	Cu	Fe
	Units	kg	ppm	%	ppm	ppm	ppm	ppm	%	ppm	ppm	ppm	ppm	ppm	ppm	%
	LOR	0.02	0.01	0.01	0.2	10	0.05	0.01	0.01	0.02	0.01	0.1	1	0.05	0.2	0.01
C385589		0.58	0.44	4.41	78.9	530	2.36	0.29	1.1	1.37	33.3	14.5	46	4.16	59.2	5.1
C385590		0.54	0.2	2.13	29.4	310	1.09	0.1	1.21	0.63	17.85	7	33	2.24	33	2.81
C385591		0.54	0.38	5.25	73.4	800	2.48	0.19	0.36	1.98	46.1	13.5	45	4.44	59.5	5.34
C385593		1.22	0.1	0.1	6	30	0.09	0.04	21	0.07	1.27	1.2	2	0.17	1.9	0.48
C385594		0.54	0.28	3.05	41.1	470	1.63	0.11	0.68	0.89	21.3	7.5	33	2.66	38.5	3.48
C385595		0.50	0.48	2.03	22.9	120	1.02	0.12	0.29	1.27	21.8	6.6	42	2.14	32.6	2.97
C385596		1.08	0.01	0.06	8	20	0.07	0.01	20.9	0.06	1.53	1.2	2	0.16	2.3	0.44
C385597		0.60	0.49	1.9	19.6	90	1.02	0.11	0.67	1.72	25.6	6.1	36	2.06	33.2	2.44
C385598		2.62	0.56	2.25	10.7	170	1.19	0.1	0.18	6.14	22.5	4.5	49	2.65	48	1.57
C385599		2.40	0.6	1.69	11.9	350	1.01	0.07	0.92	10.05	18.9	3.5	52	2.2	43.9	1.41
C385600		1.68	0.56	1.56	11.9	300	0.96	0.07	0.17	8.38	16.1	3.2	56	1.95	48.6	0.93
C488151		1.16	0.02	0.07	5	30	0.07	0.01	21.1	0.1	1.67	1.3	8	0.22	2.4	0.45
C488152		1.72	0.57	1.49	12.8	270	1.11	0.07	0.27	8.63	17.3	3.5	64	1.87	49.8	1.28
C488153		1.22	0.39	1.56	10.8	280	1.06	0.07	0.62	2.32	16.75	3.5	36	1.98	32.4	1.3
C488154		0.96	0.42	1.67	11.6	190	1.17	0.08	0.07	2.41	18.75	4.1	51	2.1	40.6	1.55
C488155		0.82	0.99	2.25	15.2	150	1.57	0.11	0.11	2.05	25.9	5.5	50	2.52	43.6	1.66
C488156		0.92	0.46	1.17	8.6	360	0.8	0.06	0.2	1.01	12.9	2.9	46	1.3	26.5	1.29
C488157		0.28	0.53	1.83	21.5	160	0.83	0.09	0.39	2.39	13.5	4.6	44	2.01	43.5	1.61
C488159		1.20	0.01	0.06	<5	20	0.08	0.01	21.3	0.06	1.55	1.3	2	0.15	1.6	0.42
C488160		0.90	0.89	6.87	68.9	70	3.1	0.27	0.64	7.6	51.2	14.4	97	9.82	61.8	3.49
C488161		0.92	0.71	5.66	37.2	230	2.23	0.19	1.46	6.51	54.2	10.5	75	7.09	49.5	2.72
C488162		0.92	0.45	3.42	24.3	360	1.26	0.13	4.19	3.24	39.6	7.2	64	4.2	31	2.03
C488163		1.66	0.39	3.86	18.1	360	1.32	0.13	4.94	3.67	44.4	7.2	54	4.54	27.2	1.73
C488164		1.78	0.35	5.66	24.9	190	1.92	0.2	2.76	3.93	43.4	11.2	62	7.23	37.1	2.86
C488165		1.86	0.33	5.32	20.8	200	1.73	0.18	2.12	3.36	38.1	10.2	67	6.57	35.9	2.46
C488166		2.60	0.29	3.47	18.9	210	1.17	0.17	2.3	3.19	32.7	7.8	53	4.49	32.7	1.92
C488167		2.56	0.24	3.06	16.1	480	1.17	0.11	4.63	2.98	34.9	6.4	53	3.57	33.3	1.62
C488168		0.20	0.29	5.89	22	300	1.88	0.16	2.07	0.62	58.6	12.3	74	7.07	32.6	2.55
C488169		0.08	0.51	1.24	101.5	30	0.21	0.1	0.43	1.81	8.65	3.2	14	0.91	78.3	28.8
C488170		0.20	0.41	6.24	24	100	2.02	0.19	0.9	0.96	59.3	13.5	83	8.03	41.5	3.32

Comments: Interference: Ca>10% on ICP-MS As,ICP-AES results shown. REE's may not be totally soluble in MS61 method.

ALS Chemex

EXCELLENCE IN ANALYTICAL CHEMISTRY

ALS Canada Ltd.

212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO-RICH

Finalized Date: 25-SEP-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07087265

Sample Description	Method	ME-MS61	ME-MS61	ME-MS61	Hg-CV41	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61
	Analyte	Ga	Ge	Hf	Hg	In	K	La	Li	Mg	Mn	Mo	Na	Nb	Ni	P
	Units	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	%	ppm	ppm	%	ppm	ppm	ppm
	LOR	0.05	0.05	0.1	0.01	0.005	0.01	0.5	0.2	0.01	5	0.05	0.01	0.1	0.2	10
C385589		11.9	0.23	2.4	0.40	0.067	1.52	15	10.8	0.76	182	50.8	0.06	8.3	113.5	370
C385590		5.82	0.12	1.4	0.20	0.03	0.73	8.9	7.6	0.73	165	25.6	0.04	4.5	64.4	150
C385591		13.2	0.24	2.9	0.37	0.072	1.67	19.7	13.4	0.41	204	77.7	0.05	12	193	410
C385593		0.38	0.1	<0.1	<0.01	<0.005	0.04	0.7	1.3	13.15	209	0.37	0.01	0.2	1	180
C385594		8.03	0.14	2	0.24	0.027	0.88	9.9	8.2	0.44	177	44.5	0.04	4.7	112	470
C385595		6.04	0.1	1.4	0.14	0.027	0.66	8.7	7.8	0.23	98	39.9	0.04	4.4	122	190
C385596		0.26	0.05	<0.1	<0.01	<0.005	0.02	0.6	1.1	13.3	195	0.19	<0.01	0.2	2.4	190
C385597		5.87	0.1	1.5	0.12	0.027	0.59	10.2	8.6	0.41	113	33.7	0.03	5.2	104.5	220
C385598		6.53	0.13	0.9	0.13	0.021	0.74	11.8	7.4	0.18	75	50	0.04	4.2	136.5	280
C385599		5.41	0.12	0.7	0.10	0.021	0.55	10.5	7	0.32	91	38.2	0.04	3.4	123.5	500
C385600		4.74	0.11	0.7	0.15	0.017	0.52	9.1	7.6	0.13	40	44.7	0.04	3.1	129	160
C488151		0.32	0.06	<0.1	<0.01	<0.005	0.03	0.7	1.3	13.25	202	0.44	0.01	0.3	3.3	170
C488152		4.61	0.11	0.7	0.10	0.016	0.48	9.8	8.5	0.2	61	38	0.03	3.1	131	170
C488153		4.38	0.11	0.6	0.06	0.013	0.5	8.6	8.9	0.36	91	35.4	0.03	3	121.5	120
C488154		4.77	0.11	0.7	0.07	0.015	0.54	10.1	12.6	0.1	72	42	0.03	3.4	146	180
C488155		6.55	0.13	1	0.09	0.022	0.69	13.4	8.8	0.14	72	50.7	0.03	4.8	211	220
C488156		2.93	0.08	0.5	0.05	0.008	0.34	6.6	9.3	0.12	77	28.8	0.03	2.4	105	180
C488157		6.86	0.17	0.9	0.11	0.017	0.55	6	5.2	0.12	75	44.8	0.03	3.9	190.5	180
C488159		0.26	0.05	<0.1	<0.01	<0.005	0.02	0.6	1.2	13.6	209	0.26	0.01	0.3	2.9	180
C488160		25.3	0.44	2.7	0.20	0.137	2.04	20.8	13.4	0.54	104	90.2	0.06	11.5	580	2680
C488161		16.9	0.27	2.3	0.19	0.079	1.71	31.1	11.2	0.5	118	40.4	0.05	9.6	152.5	420
C488162		9.84	0.18	1.4	0.10	0.041	1.05	19	8	0.34	134	26.6	0.05	5.8	103.5	170
C488163		10.9	0.15	1.4	0.11	0.037	1.2	21.1	7.1	0.37	112	21.5	0.06	6	86.9	410
C488164		15.95	0.19	2.3	0.14	0.044	1.79	24.9	8.1	0.51	114	37	0.12	9.6	114	340
C488165		14.2	0.16	2	0.13	0.041	1.68	22.1	7.3	0.44	95	38.1	0.09	8.4	129.5	250
C488166		9.76	0.16	1.7	0.11	0.038	1.11	20	5.6	0.61	128	39.2	0.06	6.3	132.5	210
C488167		8.1	0.15	1.6	0.08	0.029	1	21.9	5	0.27	102	40.6	0.07	5.9	131.5	280
C488168		16.1	0.16	3.2	0.11	0.038	1.96	33.1	7	0.41	102	39.5	0.22	11.4	120	700
C488169		2.86	0.65	0.7	0.18	0.013	0.31	4.3	1	0.06	52	8.1	0.3	2.7	50	40
C488170		17.35	0.15	3.4	0.12	0.043	2.09	32.7	7.5	0.44	96	40.9	0.17	12	137	490

Comments: Interference: Ca>10% on ICP-MS As,ICP-AES results shown. REE's may not be totally soluble in MS61 method.

ALS Chemex

EXCELLENCE IN ANALYTICAL CHEMISTRY

ALS Canada Ltd.

212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO-RICH

Finalized Date: 25-SEP-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07087265

Sample Description	Method	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61
	Analyte	Pb	Rb	Re	S	Sb	Sc	Se	Sn	Sr	Ta	Te	Th	Ti	Tl	U
	Units	ppm	ppm	ppm	%	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm
	LOR	0.5	0.1	0.002	0.01	0.05	0.1	1	0.2	0.2	0.05	0.05	0.2	0.005	0.02	0.1
C385589		13.3	75	0.049	5.64	2.62	12.5	8	1.6	80.4	0.48	0.22	5	0.26	4.65	10.5
C385590		7.2	36.9	0.022	2.63	1.13	5.8	4	0.9	86.6	0.26	0.07	3	0.13	2.33	5.7
C385591		13.3	81.1	0.146	5.87	3.55	15.1	11	1.6	58.9	1.17	0.18	5.8	0.293	4.8	15.2
C385593		2.2	1.4	<0.002	0.03	0.08	0.7	1	<0.2	42.8	<0.05	<0.05	<0.2	<0.005	0.03	1.1
C385594		9	48.6	0.044	3.44	2.47	8.3	7	1.1	67.8	0.31	0.11	3.2	0.136	3.69	9.2
C385595		8.2	34.5	0.043	2.81	2.37	5.6	9	0.9	42.8	0.29	0.1	2.8	0.12	3.29	7.9
C385596		1.7	1	<0.002	0.02	0.07	0.4	2	<0.2	51.6	<0.05	<0.05	<0.2	<0.005	<0.02	0.6
C385597		8.3	34.1	0.034	2.51	2.47	5.7	8	0.8	67.6	0.46	0.11	2.9	0.111	2.9	7.8
C385598		7.2	47.3	0.049	1.23	17.6	5.3	15	1	54.8	0.25	0.13	3	0.109	3.23	9.1
C385599		5.7	35.9	0.061	1.01	17.6	4.1	17	0.8	100.5	0.21	0.14	2.3	0.085	2.55	8.1
C385600		6	32.6	0.058	0.92	20.9	3.8	15	0.7	42.9	0.2	0.14	2.2	0.082	3.09	8.8
C488151		2.1	1.6	<0.002	0.03	0.15	0.6	2	<0.2	54.2	<0.05	<0.05	<0.2	<0.005	0.02	1.1
C488152		5.6	30.7	0.042	1.08	14.3	4	13	0.7	47.6	0.19	0.14	2.1	0.078	3.53	7.3
C488153		6	31.9	0.038	1.2	8.04	4	11	0.7	73.1	0.19	0.1	2.1	0.079	2.39	7.6
C488154		5.8	35.2	0.045	1.13	7.19	4.3	12	0.7	40.7	0.2	0.11	2.2	0.083	3.07	9
C488155		8.4	45.6	0.093	1.4	7.34	5.8	14	0.9	42.3	0.29	0.17	3.1	0.114	3.71	10.8
C488156		4.9	21.3	0.032	0.8	3.02	2.7	8	0.7	44.6	0.15	0.07	1.7	0.054	1.71	6.3
C488157		7.1	34.1	0.057	1.39	5.56	4.6	33	0.7	35.3	0.25	0.23	2.6	0.109	4.99	12.4
C488159		1.7	1	<0.002	0.02	<0.05	0.4	2	<0.2	53.3	<0.05	<0.05	<0.2	<0.005	0.02	0.6
C488160		15.3	124.5	0.276	4.05	17.5	14.3	81	2.8	204	0.74	0.41	5.8	0.321	12	17.9
C488161		14.5	94.2	0.041	3.17	11.7	11.4	41	2.1	64.6	0.65	0.09	7.4	0.291	5.78	8.9
C488162		8.6	68.6	0.031	1.97	6.74	7.3	23	1.3	124	0.38	0.06	4.7	0.171	3.71	5.5
C488163		9.2	77.8	0.021	2.04	5.8	7.8	16	1.3	168	0.39	0.06	4.9	0.184	3.51	4.1
C488164		13.7	116.5	0.024	2.8	7.54	11.8	18	2	112.5	0.63	0.08	7.7	0.258	4.69	5.6
C488165		11.9	105.5	0.03	2.39	5.7	10.7	13	1.8	84.3	0.54	0.08	6.6	0.235	4.81	5.7
C488166		9.2	74.1	0.039	1.87	4.77	8.2	12	1.4	120	0.4	0.08	5	0.165	4.65	6.7
C488167		8.3	61.8	0.039	1.53	4.13	7.2	9	1.2	171	0.37	0.08	4.9	0.156	3.83	8
C488168		12.4	113.5	0.028	2.45	3.92	11.9	9	2.1	128.5	0.74	0.07	9.1	0.325	4.11	7.5
C488169		45.7	17.4	0.004	>10.0	12.55	1.8	83	0.7	61.4	0.14	0.12	1.4	0.064	5.58	1.8
C488170		16.6	124	0.032	3.18	5.68	13.1	10	2.3	95.7	0.8	0.09	9.7	0.343	5.07	9.2

Comments: Interference: Ca>10% on ICP-MS As,ICP-AES results shown. REE's may not be totally soluble in MS61 method.

ALS Chemex
EXCELLENCE IN ANALYTICAL CHEMISTRY
ALS Canada Ltd.
212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: STRATEGIC METALS LTD.
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO-RICH

Finalized Date: 25-SEP-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07087265

Sample Description	Method / Analyte / Units / LOR	ME-MS61 V ppm 1	ME-MS61 W ppm 0.1	ME-MS61 Y ppm 0.1	ME-MS61 Zn ppm 2	ME-MS61 Zr ppm 0.5
C385589		168	1	20.2	155	79.9
C385590		110	0.5	12.5	77	46.8
C385591		293	1	19.2	273	96.8
C385593		5	0.1	0.9	16	0.6
C385594		246	0.5	16.4	98	58.3
C385595		404	0.5	14.4	178	54.1
C385596		1	0.1	0.9	16	0.5
C385597		355	0.5	14.1	224	51.3
C385598		821	0.6	13.4	546	39.9
C385599		877	0.4	18.6	809	32.9
C385600		749	0.4	11.3	693	31.2
C488151		5	0.1	1	20	0.7
C488152		637	0.4	15.2	607	34
C488153		485	0.4	21.9	239	31
C488154		461	0.5	16.9	240	37.3
C488155		568	5.5	15.3	234	46
C488156		249	2.7	8	125	24.6
C488157		663	1.5	10.8	448	41.7
C488159		1	0.1	0.9	16	0.6
C488160		1460	1.5	21.3	957	94.8
C488161		897	1.4	22.9	666	80.6
C488162		576	0.8	24.1	272	51
C488163		538	0.8	31.2	298	41.9
C488164		696	1.1	26.2	314	78.2
C488165		730	0.9	17.6	290	69.2
C488166		632	0.7	14.7	243	59.7
C488167		655	0.7	26.4	230	59.1
C488168		651	1.3	20	50	103.5
C488169		116	0.3	3.3	86	22.3
C488170		775	1.4	16.1	70	109.5

Comments: Interference: Ca>10% on ICP-MS As,ICP-AES results shown. REE's may not be totally soluble in MS61 method.

ALS Chemex
EXCELLENCE IN ANALYTICAL CHEMISTRY
ALS Canada Ltd.
212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Finalized Date: 26-JUL-2007
Account: MTT

CERTIFICATE VA07078518

Project: NIMO

P.O. No.:

This report is for 4 Rock samples submitted to our lab in Vancouver, BC, Canada on 20-JUL-2007.

The following have access to data associated with this certificate:

AL ARCHER VANCOUVER OFFICE	DOUG EATON BILL WENGZYNOWSKI	JOAN MARIACHER

SAMPLE PREPARATION

ALS CODE	DESCRIPTION
FND-02	Find Sample for Addn Analysis

ANALYTICAL PROCEDURES

ALS CODE	DESCRIPTION	INSTRUMENT
ME-MS42	Up to 34 elements by ICP-MS	ICP-MS

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

is is the Final Report and supersedes any preliminary report with this certificate number. Results apply to samples as submitted. All ges of this report have been checked and approved for release.

Signature: Lawrence Ng

Lawrence Ng, Laboratory Manager - Vancouver

ALS Chemex
EXCELLENCE IN ANALYTICAL CHEMISTRY
ALS Canada Ltd.
212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: STRATEGIC METALS LTD.
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO

Finalized Date: 26-JUL-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07078518

Sample Description	Method Analyte Units LOR	ME-MS42 Re ppm 0.001
C385603		33.5
C385617		49.9
C385624		48.3
C385626		NSS

Comments: NSS is non-sufficient sample.

ALS Chemex
EXCELLENCE IN ANALYTICAL CHEMISTRY
ALS Canada Ltd.
212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

o: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Finalized Date: 27-JUL-2007
Account: MTT

CERTIFICATE VA07077183

Project: NIMO

P.O. No.:

This report is for 193 Soil samples submitted to our lab in Vancouver, BC, Canada on 17-JUL-2007.

The following have access to data associated with this certificate:

JOAN MARIACHER

SAMPLE PREPARATION

ALS CODE	DESCRIPTION
WEI-21	Received Sample Weight
LOG-22	Sample login - Rcd w/o BarCode
SCR-41	Screen to -180um and save both

ANALYTICAL PROCEDURES

ALS CODE	DESCRIPTION
ME-MS41	51 anal. aqua regia ICPMS

To: **STRATEGIC METALS LTD.**
ATTN: JOAN MARIACHER
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

is is the Final Report and supersedes any preliminary report with this certificate number. Results apply to samples as submitted. All ges of this report have been checked and approved for release.

Signature:

Lawrence Ng, Laboratory Manager - Vancouver

ALS Chemex

EXCELLENCE IN ANALYTICAL CHEMISTRY

ALS Canada Ltd.

212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: STRATEGIC METALS LTD.
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO

Finalized Date: 27-JUL-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07077183

Sample Description	Method	WEI-21	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41
	Analyte	Recvd Wt.	Ag	Al	As	Au	B	Ba	Be	Bi	Ca	Cd	Ce	Co	Cr	Cs
	Units	kg	ppm	%	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppm	ppm	ppm
	LOR	0.02	0.01	0.01	0.1	0.2	10	10	0.05	0.01	0.01	0.01	0.02	0.1	1	0.05
CC39510		0.08	1.11	1.06	14.8	<0.2	<10	3780	0.64	0.20	0.87	5.39	32.70	6.7	24	0.91
CC39511		0.06	2.23	0.94	10.9	<0.2	<10	1360	0.44	0.14	0.24	18.80	16.60	1.9	29	1.18
CC39512		0.04	1.50	0.57	6.3	<0.2	<10	50	0.14	0.06	0.06	1.23	6.21	1.3	17	0.97
CC39513		0.06	0.58	1.33	13.7	<0.2	<10	740	0.58	0.18	0.17	10.80	18.65	9.3	25	0.98
CC39514		0.14	0.35	1.28	20.5	<0.2	<10	870	0.62	0.25	0.17	3.38	20.30	13.4	26	0.88
CC39515		0.12	0.15	1.54	33.1	<0.2	<10	900	1.00	0.24	0.36	2.74	24.10	22.2	29	0.88
CC39516		0.18	0.15	1.81	14.1	<0.2	<10	250	0.73	0.22	0.11	0.35	12.05	11.1	32	1.52
CC39517		0.08	0.07	1.72	20.1	<0.2	<10	190	0.67	0.21	0.15	0.27	6.64	13.0	31	1.21
CC39518		0.20	0.21	1.25	15.9	<0.2	<10	1100	0.70	0.17	0.26	2.04	18.70	12.6	24	0.95
CC39519		0.16	0.30	1.51	17.7	<0.2	<10	1020	0.75	0.22	0.32	2.14	23.90	32.4	28	0.95
CC39520		0.12	0.30	1.52	14.4	<0.2	<10	1030	0.85	0.21	0.39	3.49	21.90	21.1	27	1.03
CC39521		0.14	0.27	1.39	13.7	<0.2	<10	1160	0.76	0.19	0.36	5.33	19.75	27.2	24	1.09
CC39522		0.10	0.32	1.51	17.2	<0.2	<10	1310	0.78	0.22	0.38	3.65	19.90	11.3	28	1.23
CC39523		0.18	0.30	1.60	17.7	<0.2	<10	1020	0.74	0.23	0.27	1.76	20.60	9.4	29	1.43
CC39524		0.16	0.35	1.54	17.5	<0.2	<10	1280	0.84	0.22	0.27	2.48	20.70	11.7	29	1.30
CC39525		0.04	0.41	1.48	24.0	<0.2	<10	1350	0.74	0.22	0.35	2.23	21.20	10.6	27	1.17
CC39526		0.10	0.42	1.75	9.4	<0.2	<10	1130	0.86	0.27	0.43	4.34	16.80	6.6	28	1.80
CC39527		0.08	0.48	1.36	20.2	<0.2	<10	1720	1.27	0.20	0.31	6.51	25.60	12.3	20	0.98
CC39528		0.14	0.61	1.30	16.0	<0.2	<10	1960	1.10	0.22	0.42	9.18	25.70	8.6	24	1.07
CC39529		0.02	0.78	1.13	14.4	<0.2	<10	2350	1.12	0.19	0.30	10.80	30.50	8.7	22	0.93
CC39530		0.08	0.68	1.15	9.0	<0.2	10	530	1.04	0.11	5.43	2.59	34.80	6.4	26	1.24
CC39531		0.14	0.63	1.06	8.0	<0.2	10	370	0.83	0.09	7.95	2.89	32.20	6.1	22	1.20
CC39532		0.10	0.77	1.10	9.5	<0.2	10	270	0.98	0.10	7.60	2.62	34.60	6.7	23	1.30
CC39533		0.08	0.73	0.95	8.5	<0.2	10	270	0.87	0.11	7.36	4.52	33.30	6.2	20	1.14
CC39534		0.10	0.36	1.09	6.5	<0.2	10	420	0.71	0.07	8.58	1.31	33.90	5.0	24	1.00
CC39535		0.08	0.80	1.05	8.1	<0.2	10	330	0.89	0.16	4.31	2.83	37.60	8.1	21	0.94
CC39536		0.10	0.87	1.18	8.7	<0.2	10	370	0.96	0.17	4.62	2.78	40.10	8.0	24	1.06
CC39537		0.14	0.51	1.11	6.8	<0.2	10	340	0.75	0.12	5.97	1.75	38.40	6.9	22	1.09
CC39538		0.02	0.61	1.11	6.7	<0.2	10	390	0.78	0.16	1.40	1.99	40.10	8.1	22	0.94
CC39539		0.20	0.52	1.10	11	<0.2	10	170	0.85	0.08	12.55	1.73	38.50	5.8	25	1.11
CC39540		0.08	0.80	1.12	7.0	<0.2	10	510	0.92	0.11	3.49	3.04	31.10	6.0	25	1.14
CC39541		0.02	0.55	1.14	13.2	<0.2	10	830	0.83	0.12	3.66	2.69	33.20	7.3	26	1.18
CC39542		0.12	0.46	1.13	15.5	<0.2	10	980	0.79	0.14	3.39	2.74	32.80	8.6	27	1.06
CC39543		0.04	0.53	1.12	8.1	<0.2	10	600	0.77	0.11	4.22	2.36	31.70	6.1	25	1.19
CC39544		0.14	0.49	1.21	11.6	<0.2	<10	620	0.80	0.15	3.59	2.46	31.30	8.9	24	1.12
CC39545		0.10	0.05	0.37	7.1	<0.2	<10	120	0.31	0.10	0.09	0.15	12.25	5.3	6	0.66
CC39546		0.02	0.08	0.57	7.7	<0.2	<10	170	0.49	0.12	0.13	0.20	15.10	10.3	8	0.85
CC39547		0.18	0.05	0.49	6.6	<0.2	<10	190	0.31	0.10	0.10	0.09	10.90	2.7	8	0.69
CC39548		0.18	0.09	0.87	8.4	<0.2	<10	280	0.47	0.14	0.17	0.25	13.75	9.8	14	1.07
CC39549		0.10	0.10	0.60	10.5	<0.2	<10	380	0.41	0.12	0.13	0.22	13.55	7.1	10	0.93

Comments: Interference: Ca>10% on ICP-MS As,ICP-AES results shown. Gold determinations by ME-MS41 are semi-quantitative due to the small sample weight used (0.5g).

ALS Chemex

EXCELLENCE IN ANALYTICAL CHEMISTRY

ALS Canada Ltd.

212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: STRATEGIC METALS LTD.
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO

Finalized Date: 27-JUL-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07077183

Sample Description	Method	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41
	Analyte	Cu	Fe	Ga	Ge	Hf	Hg	In	K	La	Li	Mg	Mn	Mo	Na	Nb
	Units	ppm	%	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	%	ppm	ppm	%	ppm
	LOR	0.2	0.01	0.05	0.05	0.02	0.01	0.005	0.01	0.2	0.1	0.01	5	0.05	0.01	0.05
CC39510		49.1	2.53	2.97	0.08	0.07	0.26	0.035	0.11	18.8	8.2	0.20	183	7.02	0.02	0.23
CC39511		69.9	0.84	3.34	0.07	0.02	0.51	0.023	0.07	9.3	4.6	0.13	48	18.25	0.01	0.34
CC39512		15.1	19.95	2.12	0.16	0.02	0.33	0.008	0.05	3.3	3.4	0.09	27	12.75	0.01	0.30
CC39513		58.8	1.34	3.46	0.06	0.03	0.13	0.035	0.07	9.4	12.3	0.19	54	18.35	0.01	0.35
CC39514		46.1	2.72	3.77	0.06	0.04	0.08	0.037	0.08	10.4	16.4	0.28	96	12.35	0.01	0.35
CC39515		38.9	5.19	4.48	0.07	0.07	0.04	0.043	0.10	12.1	22.0	0.44	825	11.30	0.02	0.32
CC39516		32.4	3.89	5.30	0.05	0.04	0.09	0.044	0.10	5.5	21.5	0.43	182	2.50	0.01	0.19
CC39517		26.0	5.29	5.08	0.05	0.04	0.07	0.045	0.09	2.8	21.9	0.45	234	2.76	0.01	0.12
CC39518		28.4	3.21	3.62	0.05	0.03	0.06	0.033	0.08	9.8	15.6	0.30	178	7.09	0.01	0.22
CC39519		36.0	4.21	4.43	0.08	0.05	0.07	0.038	0.09	12.2	17.1	0.36	317	8.97	0.01	0.42
CC39520		32.6	3.17	4.39	0.06	0.05	0.08	0.035	0.09	11.0	18.1	0.37	602	5.71	0.01	0.35
CC39521		28.3	3.40	3.95	0.06	0.04	0.09	0.032	0.09	10.3	17.3	0.33	1390	6.76	0.01	0.24
CC39522		34.8	3.23	4.32	0.06	0.04	0.11	0.040	0.10	10.3	19.6	0.34	284	7.12	0.01	0.26
CC39523		29.6	3.24	4.83	0.06	0.04	0.10	0.038	0.10	10.6	18.1	0.36	137	7.56	0.01	0.30
CC39524		36.4	3.42	4.49	0.06	0.05	0.11	0.043	0.10	10.4	18.6	0.32	174	5.93	0.01	0.27
CC39525		33.3	4.63	4.16	0.07	0.04	0.12	0.038	0.09	11.0	17.9	0.31	218	11.00	0.02	0.31
CC39526		47.6	2.99	4.79	0.06	0.04	0.20	0.045	0.11	8.4	23.8	0.33	161	5.69	0.02	0.24
CC39527		42.3	3.47	3.53	0.09	0.05	0.14	0.032	0.07	13.8	18.9	0.23	250	10.10	0.03	0.32
CC39528		58.3	1.67	3.74	0.08	0.05	0.16	0.037	0.08	13.9	18.0	0.25	62	7.29	0.03	0.33
CC39529		64.8	1.42	3.13	0.09	0.05	0.20	0.032	0.08	16.9	13.5	0.18	70	6.97	0.04	0.32
CC39530		61.3	1.32	4.45	0.12	0.11	0.11	0.026	0.15	20.3	24.1	1.48	185	3.61	0.01	0.28
CC39531		57.8	1.25	4.05	0.11	0.11	0.11	0.022	0.14	18.0	23.0	1.58	239	2.97	0.01	0.26
CC39532		68.4	1.34	4.25	0.13	0.12	0.13	0.024	0.13	19.2	25.1	1.65	184	4.37	0.01	0.29
CC39533		66.7	1.13	3.91	0.11	0.12	0.11	0.024	0.13	18.6	21.7	1.39	223	3.07	0.01	0.28
CC39534		38.5	1.19	3.65	0.11	0.08	0.06	0.019	0.16	18.6	18.9	1.62	170	2.50	0.01	0.22
CC39535		74.0	1.54	3.75	0.08	0.12	0.15	0.029	0.12	21.2	17.4	0.91	375	2.46	0.01	0.29
CC39536		82.2	1.62	4.14	0.08	0.11	0.17	0.032	0.13	23.1	19.0	0.96	350	2.51	0.01	0.34
CC39537		51.3	1.44	3.98	0.10	0.10	0.10	0.023	0.15	20.6	18.3	1.07	266	2.45	0.01	0.27
CC39538		61.6	1.64	3.82	0.08	0.10	0.13	0.026	0.14	22.5	15.4	0.59	374	1.88	0.01	0.27
CC39539		52.1	1.16	4.46	0.15	0.10	0.07	0.022	0.16	21.5	25.5	1.99	213	4.06	0.01	0.26
CC39540		67.3	1.23	4.11	0.10	0.13	0.13	0.024	0.12	18.2	21.0	1.22	161	1.90	0.01	0.32
CC39541		53.7	1.57	4.22	0.09	0.10	0.09	0.027	0.15	18.3	19.8	1.18	242	5.85	0.01	0.25
CC39542		53.6	1.88	3.99	0.09	0.10	0.09	0.031	0.15	18.5	18.0	1.03	316	6.96	0.01	0.20
CC39543		49.5	1.33	3.97	0.09	0.11	0.09	0.024	0.13	18.0	19.7	1.22	168	3.03	0.01	0.24
CC39544		50.1	1.80	4.14	0.10	0.11	0.09	0.030	0.12	17.8	20.4	1.12	218	4.09	0.01	0.20
CC39545		10.4	1.26	1.16	<0.05	0.02	0.03	0.019	0.05	5.3	5.6	0.07	134	0.62	<0.01	0.11
CC39546		14.4	1.55	1.59	0.05	0.03	0.04	0.023	0.07	6.2	9.1	0.12	204	0.72	<0.01	0.14
CC39547		9.3	1.46	1.20	<0.05	<0.02	0.03	0.018	0.06	4.7	4.9	0.09	74	0.55	<0.01	0.12
CC39548		17.0	1.83	2.64	<0.05	0.02	0.09	0.026	0.07	5.9	13.7	0.19	364	2.28	<0.01	0.17
CC39549		16.0	1.92	1.87	<0.05	0.02	0.16	0.022	0.07	5.9	9.4	0.13	212	3.90	<0.01	0.12

Comments: Interference: Ca>10% on ICP-MS As,ICP-AES results shown. Gold determinations by ME-MS41 are semi-quantitative due to the small sample weight used (0.5g).

ALS Chemex

EXCELLENCE IN ANALYTICAL CHEMISTRY

ALS Canada Ltd.

212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: STRATEGIC METALS LTD.
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO

Finalized Date: 27-JUL-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07077183

Sample Description	Method	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41
	Analyte	Ni	P	Pb	Rb	Re	S	Sb	Sc	Se	Sn	Sr	Ta	Te	Th	Ti
	Units	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%
	LOR	0.2	10	0.2	0.1	0.001	0.01	0.05	0.1	0.2	0.2	0.2	0.01	0.01	0.2	0.005
CC39510		48.2	910	12.8	13.0	0.018	0.14	2.91	5.1	5.5	0.4	83.2	0.01	0.07	3.2	0.005
CC39511		39.8	720	9.5	10.0	0.061	0.17	6.50	2.9	12.3	0.4	43.3	<0.01	0.06	0.7	0.011
CC39512		28.1	610	3.2	7.4	0.027	2.05	5.92	2.1	7.9	0.3	16.4	<0.01	0.05	0.9	0.010
CC39513		116.5	570	11.2	10.4	0.018	0.34	3.55	4.0	6.3	0.4	29.6	<0.01	0.04	1.9	0.006
CC39514		82.9	630	13.3	10.0	0.011	0.16	2.70	4.8	4.1	0.4	40.3	<0.01	0.06	3.1	0.006
CC39515		67.0	850	21.5	10.4	0.004	0.07	2.54	5.5	2.7	0.5	56.1	<0.01	0.08	4.5	0.007
CC39516		39.9	460	15.2	13.7	0.001	0.03	0.77	6.1	1.4	0.6	15.8	<0.01	0.05	3.0	<0.005
CC39517		45.9	510	17.8	10.8	0.001	0.04	0.89	5.1	1.0	0.6	17.4	<0.01	0.05	2.3	<0.005
CC39518		45.8	600	13.0	10.2	0.004	0.06	1.82	4.6	2.4	0.4	39.5	<0.01	0.05	3.2	<0.005
CC39519		98.2	680	14.6	11.9	0.005	0.07	2.21	5.5	4.4	0.5	44.1	<0.01	0.06	4.0	0.007
CC39520		54.1	590	13.3	12.9	0.005	0.09	1.68	5.2	2.9	0.5	42.2	<0.01	0.06	3.5	0.006
CC39521		71.1	560	12.2	12.2	0.006	0.07	1.59	4.7	2.9	0.4	37.0	<0.01	0.04	3.2	0.005
CC39522		63.0	640	14.8	13.7	0.009	0.09	1.75	5.5	3.6	0.5	43.1	<0.01	0.06	3.4	<0.005
CC39523		37.3	570	14.7	14.6	0.005	0.06	1.76	5.0	2.9	0.5	31.4	<0.01	0.06	3.4	0.005
CC39524		48.0	670	15.0	13.7	0.007	0.11	1.87	5.9	3.8	0.5	37.3	<0.01	0.05	3.6	<0.005
CC39525		44.1	620	13.5	13.6	0.007	0.10	2.21	5.0	4.3	0.5	42.4	<0.01	0.07	3.4	<0.005
CC39526		40.5	560	18.0	16.6	0.010	0.16	1.38	6.2	3.8	0.6	43.0	0.01	0.05	3.0	<0.005
CC39527		57.7	580	12.4	13.4	0.013	0.14	2.93	4.8	6.3	0.4	47.8	<0.01	0.06	3.8	0.005
CC39528		66.5	640	13.4	14.3	0.017	0.21	2.99	5.7	7.1	0.4	55.7	<0.01	0.05	3.6	0.005
CC39529		74.0	710	12.0	12.7	0.025	0.18	3.25	5.0	8.5	0.4	52.1	<0.01	0.06	3.5	0.006
CC39530		36.7	2650	8.7	19.4	0.004	0.08	2.27	3.9	3.2	0.4	239.0	<0.01	0.05	2.6	0.008
CC39531		33.1	2590	8.1	18.7	0.002	0.07	2.02	3.6	2.9	0.4	359.0	<0.01	0.05	2.3	0.008
CC39532		68.4	2270	9.0	19.6	0.003	0.08	2.17	4.1	3.6	0.4	331.0	<0.01	0.05	2.2	0.009
CC39533		41.4	2150	8.8	17.2	0.002	0.07	2.26	3.8	3.2	0.4	348.0	<0.01	0.05	2.1	0.008
CC39534		21.4	3980	6.6	16.5	0.001	0.04	1.57	2.9	1.7	0.3	367.0	<0.01	0.04	3.0	0.008
CC39535		36.2	2180	11.4	16.0	0.005	0.08	1.83	4.0	3.3	0.4	189.5	<0.01	0.06	2.3	0.008
CC39536		38.7	2280	12.0	17.7	0.004	0.08	1.82	4.4	3.3	0.4	205.0	<0.01	0.07	2.3	0.009
CC39537		28.8	2920	8.8	17.5	0.002	0.05	1.47	3.7	2.3	0.4	246.0	<0.01	0.05	2.9	0.009
CC39538		35.5	2360	10.6	15.3	0.003	0.06	1.28	3.7	2.5	0.4	57.7	<0.01	0.06	2.9	0.008
CC39539		24.1	3990	7.8	18.5	0.002	0.04	2.40	3.4	2.5	0.4	562.0	<0.01	0.05	2.6	0.008
CC39540		37.0	2190	8.6	16.7	0.007	0.11	1.95	3.9	3.7	0.4	155.0	<0.01	0.05	2.6	0.010
CC39541		41.0	2340	9.6	18.2	0.004	0.07	2.75	3.8	2.8	0.4	174.5	<0.01	0.06	3.3	0.007
CC39542		45.2	2100	10.8	17.2	0.005	0.07	2.90	3.8	2.7	0.4	167.0	<0.01	0.07	3.6	0.005
CC39543		34.6	2790	8.3	17.6	0.004	0.07	1.78	3.5	2.5	0.4	188.0	<0.01	0.05	3.0	0.007
CC39544		42.2	2470	10.3	15.8	0.004	0.07	2.00	4.0	2.5	0.4	176.5	<0.01	0.05	3.4	0.005
CC39545		12.2	280	7.5	6.9	<0.001	0.03	0.21	1.7	0.7	0.2	14.9	<0.01	0.03	2.4	<0.005
CC39546		17.1	460	8.8	8.4	<0.001	0.04	0.24	2.4	3.6	0.2	19.2	<0.01	0.03	2.2	<0.005
CC39547		8.8	340	7.4	7.1	<0.001	0.03	0.16	1.6	0.6	0.2	14.0	<0.01	0.02	1.9	<0.005
CC39548		21.6	420	10.2	11.6	0.001	0.03	0.32	2.8	1.2	0.3	18.7	<0.01	0.03	2.4	<0.005
CC39549		18.2	460	8.1	9.3	0.003	0.04	0.40	2.3	2.1	0.3	18.5	<0.01	0.03	2.3	<0.005

Comments: Interference: Ca>10% on ICP-MS As,ICP-AES results shown. Gold determinations by ME-MS41 are semi-quantitative due to the small sample weight used (0.5g).

ALS Chemex

EXCELLENCE IN ANALYTICAL CHEMISTRY

ALS Canada Ltd.

212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: STRATEGIC METALS LTD.
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO

Finalized Date: 27-JUL-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07077183

Sample Description	Method	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41
	Analyte	Tl	U	V	W	Y	Zn	Zr
	Units	ppm	ppm	ppm	ppm	ppm	ppm	ppm
	LOR	0.02	0.05	1	0.05	0.05	2	0.5
CC39510		0.46	4.00	174	0.10	19.35	355	1.7
CC39511		1.92	4.80	299	0.12	10.80	312	0.5
CC39512		1.22	1.20	299	0.08	7.61	113	<0.5
CC39513		0.67	2.77	180	0.11	13.25	263	0.8
CC39514		0.45	2.56	128	0.10	13.65	224	1.1
CC39515		0.30	1.75	121	0.12	11.75	275	2.4
CC39516		0.24	0.68	52	<0.05	7.46	124	1.0
CC39517		0.18	0.39	48	<0.05	5.53	131	1.0
CC39518		0.32	2.02	103	0.10	9.68	226	1.2
CC39519		0.41	4.71	92	0.10	12.55	399	1.4
CC39520		0.40	2.03	93	0.12	11.35	271	1.5
CC39521		0.38	1.95	94	0.09	9.61	277	0.9
CC39522		0.42	2.26	108	0.10	10.25	288	1.1
CC39523		0.42	1.75	100	0.08	8.66	210	1.0
CC39524		0.46	2.42	107	0.09	11.25	266	1.2
CC39525		0.47	2.61	123	0.09	10.55	278	1.1
CC39526		0.59	1.80	85	0.06	10.25	237	1.0
CC39527		0.49	3.86	123	0.13	16.50	297	1.2
CC39528		0.50	4.52	135	0.08	15.25	310	1.1
CC39529		0.59	5.88	166	0.09	18.90	339	1.2
CC39530		0.29	2.46	135	0.06	19.85	235	3.4
CC39531		0.25	2.05	111	0.06	18.35	246	3.0
CC39532		0.50	4.07	107	0.07	20.00	275	3.3
CC39533		0.22	2.23	100	0.06	19.50	300	3.2
CC39534		0.12	2.14	118	0.07	17.75	177	2.7
CC39535		0.16	2.15	82	0.07	20.60	194	2.9
CC39536		0.18	2.33	89	0.08	21.80	198	2.7
CC39537		0.15	2.10	93	0.06	18.95	182	2.4
CC39538		0.16	2.10	79	0.07	18.60	185	2.4
CC39539		0.13	2.68	131	0.05	21.10	200	3.1
CC39540		0.32	2.27	129	0.05	17.50	265	3.7
CC39541		0.38	2.84	170	0.07	17.25	286	3.3
CC39542		0.39	2.85	174	0.07	16.70	299	3.3
CC39543		0.33	2.40	134	0.06	17.15	245	3.1
CC39544		0.32	2.30	122	0.05	16.60	270	3.3
CC39545		0.05	0.39	13	<0.05	4.71	40	<0.5
CC39546		0.07	0.51	17	0.05	7.94	63	<0.5
CC39547		0.05	0.39	17	<0.05	4.23	34	<0.5
CC39548		0.22	0.53	27	<0.05	6.25	63	<0.5
CC39549		0.44	0.63	22	0.05	5.93	57	0.5

Comments: Interference: Ca>10% on ICP-MS As,ICP-AES results shown. Gold determinations by ME-MS41 are semi-quantitative due to the small sample weight used (0.5g).

ALS Chemex

EXCELLENCE IN ANALYTICAL CHEMISTRY

ALS Canada Ltd.

212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: STRATEGIC METALS LTD.
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO

Finalized Date: 27-JUL-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07077183

Sample Description	Method	WEI-21	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41
	Analyte	Recvd Wt.	Ag	Al	As	Au	B	Ba	Be	Bi	Ca	Cd	Ce	Co	Cr	Cs
	Units	kg	ppm	%	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppm	ppm	ppm
	LOR	0.02	0.01	0.01	0.1	0.2	10	10	0.05	0.01	0.01	0.01	0.02	0.1	1	0.05
CC39550		0.12	0.16	0.83	16.8	<0.2	<10	570	0.71	0.17	0.30	0.85	17.35	23.2	14	1.11
CC39553		0.12	1.51	1.43	51.8	<0.2	<10	530	0.40	0.36	0.04	0.75	18.30	2.0	34	1.47
CC39554		0.14	0.19	1.03	42.2	<0.2	10	340	0.48	0.24	0.11	2.23	11.65	5.7	21	0.87
CC39555		0.12	1.45	0.36	40.8	<0.2	10	700	0.73	0.16	3.15	17.00	19.40	7.4	42	0.69
CC39556		0.04	1.57	0.27	29.1	<0.2	10	860	0.66	0.12	4.30	12.60	19.25	4.1	37	0.62
CC39557		0.08	1.13	0.28	30.5	<0.2	10	790	0.78	0.12	4.00	9.78	22.80	4.1	34	0.60
CC39558		0.06	0.21	0.29	18.2	<0.2	10	1530	0.53	0.09	3.18	17.75	12.35	5.6	11	0.45
CC39559		0.06	0.36	0.44	31.8	<0.2	10	1550	0.65	0.13	1.89	5.21	13.70	5.4	19	0.59
CC39560		0.12	0.59	0.69	18.6	<0.2	10	4950	0.71	0.19	0.77	2.69	12.55	9.1	22	0.59
CC39561		0.32	0.44	0.53	12.0	<0.2	<10	1310	0.56	0.15	8.26	1.24	23.10	6.0	16	0.95
CC39562		0.06	1.38	0.92	4.7	<0.2	10	5030	0.43	0.12	2.06	1.23	14.20	5.1	17	0.64
CC39563		0.12	2.12	1.19	5.3	<0.2	<10	7750	0.50	0.12	1.26	1.75	19.25	4.3	19	0.81
CC39564		0.10	0.92	1.09	6.1	<0.2	<10	3920	0.38	0.17	0.27	0.86	20.40	4.7	19	0.64
CC39565		0.12	1.27	1.21	6.4	<0.2	<10	5270	0.44	0.17	0.21	0.88	21.70	8.1	22	0.85
CC39566		0.10	0.49	1.20	7.4	<0.2	<10	3960	0.33	0.18	0.18	0.50	19.45	6.9	21	0.71
CC39567		0.10	0.70	1.28	7.6	<0.2	10	9660	0.85	0.17	0.65	0.71	23.80	9.3	22	0.63
CC39568		0.12	0.89	1.15	5.1	<0.2	<10	5230	0.38	0.15	0.46	1.01	12.05	4.5	22	0.78
CC39569		0.04	1.22	0.75	3.4	<0.2	10	6330	0.48	0.09	1.48	1.43	17.75	5.3	13	0.62
CC39570		0.12	2.37	1.50	5.2	<0.2	10	6210	0.71	0.18	0.90	2.51	21.40	9.3	27	1.12
CC39571		0.18	0.61	1.08	8.9	<0.2	<10	3030	0.30	0.20	0.32	0.77	15.45	7.2	22	0.50
CC39572		0.08	1.80	1.18	6.2	<0.2	<10	3840	0.54	0.15	1.57	1.02	15.60	7.2	23	0.73
CC39573		0.14	0.63	0.45	7.8	<0.2	<10	3720	0.24	0.14	0.22	0.47	7.17	4.1	16	0.64
CC39574		0.20	1.24	0.72	12.3	<0.2	<10	4270	0.45	0.20	0.26	1.04	11.80	11.4	35	0.67
CC39575		0.06	1.05	0.44	15.9	<0.2	10	600	0.58	0.09	3.11	8.04	15.85	4.3	27	0.49
CC39576		0.06	0.91	0.34	15.4	<0.2	10	520	0.60	0.09	3.97	6.29	18.80	4.0	26	0.45
CC39577		0.16	0.53	0.78	14	<0.2	10	640	0.56	0.12	11.40	2.04	24.10	7.8	15	1.76
CC39578		0.24	0.70	0.73	27.7	<0.2	10	4930	0.83	0.14	4.74	5.99	26.80	10.0	32	2.85
CC39579		0.16	0.72	0.75	29.9	<0.2	10	4770	0.85	0.15	4.20	9.90	27.90	10.9	34	3.13
CC39580		0.24	0.44	0.70	11	<0.2	10	780	0.49	0.11	11.85	1.27	23.70	7.9	15	1.37
CC39581		0.14	0.42	0.67	11	<0.2	10	650	0.53	0.10	12.35	1.21	23.10	7.4	14	1.29
CC39582		0.16	0.47	0.72	13	<0.2	<10	640	0.54	0.11	12.25	1.28	24.00	8.1	14	1.40
CC39583		0.20	0.35	0.69	11	<0.2	<10	380	0.52	0.09	13.35	1.11	24.10	6.7	13	1.25
CC39584		0.22	0.40	0.79	11	<0.2	<10	230	0.58	0.10	13.00	1.14	24.30	7.0	14	1.47
CC39585		0.14	0.31	0.74	10	<0.2	<10	210	0.54	0.08	14.00	1.11	24.40	6.2	13	1.19
CC39586		0.14	0.49	0.74	9	<0.2	<10	330	0.57	0.10	12.55	1.31	25.20	6.9	17	1.34
CC39587		0.14	0.25	0.75	12	<0.2	<10	180	0.47	0.07	15.75	0.92	22.40	6.0	13	1.15
CC39588		0.08	1.14	1.16	7.3	<0.2	10	230	0.85	0.08	3.64	4.83	32.90	6.2	31	1.67
CC39591		0.24	0.44	0.56	11.6	<0.2	10	1400	0.50	0.12	8.43	1.67	23.00	6.5	17	0.98
CC39592		0.30	0.40	0.52	10.3	<0.2	<10	1410	0.51	0.19	8.80	1.14	23.40	6.1	16	0.91
CC39593		0.22	0.50	0.58	11.1	<0.2	<10	1500	0.57	0.12	8.37	1.35	22.60	6.7	17	1.05

Comments: Interference: Ca>10% on ICP-MS As,ICP-AES results shown. Gold determinations by ME-MS41 are semi-quantitative due to the small sample weight used (0.5g).

ALS Chemex
EXCELLENCE IN ANALYTICAL CHEMISTRY
ALS Canada Ltd.
212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: STRATEGIC METALS LTD.
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO

Finalized Date: 27-JUL-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07077183

Sample Description	Method	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41
	Analyte	Cu	Fe	Ga	Ge	Hf	Hg	In	K	La	Li	Mg	Mn	Mo	Na	Nb
	Units	ppm	%	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	%	ppm	ppm	%	ppm
	LOR	0.2	0.01	0.05	0.05	0.02	0.01	0.005	0.01	0.2	0.1	0.01	5	0.05	0.01	0.05
CC39550		26.2	2.96	2.78	0.07	0.03	0.24	0.031	0.08	7.0	12.3	0.20	1125	7.60	0.01	0.15
CC39553		52.2	3.76	5.70	0.20	0.05	0.08	0.066	0.13	10.1	7.1	0.11	54	162.00	0.01	0.59
CC39554		30.9	3.00	3.56	0.07	0.02	0.05	0.036	0.12	7.4	4.3	0.06	46	47.60	<0.01	0.27
CC39555		81.7	1.23	1.81	0.12	0.15	0.50	0.023	0.06	12.0	1.7	0.15	130	45.40	0.02	0.18
CC39556		80.1	0.87	1.43	0.11	0.14	0.61	0.019	0.04	14.8	1.5	0.27	66	30.00	0.02	0.16
CC39557		73.8	1.03	1.60	0.13	0.14	0.55	0.020	0.04	20.1	1.7	0.21	84	39.60	0.02	0.19
CC39558		40.5	0.94	1.28	0.07	0.11	0.25	0.014	0.04	8.3	1.1	0.12	146	34.60	0.03	0.16
CC39559		42.6	1.60	2.02	0.06	0.10	0.28	0.022	0.05	7.7	2.4	0.20	175	32.30	0.02	0.19
CC39560		66.0	3.41	2.16	0.07	0.08	0.25	0.037	0.07	6.7	2.5	0.12	222	29.00	0.08	0.15
CC39561		66.8	1.33	2.01	0.07	0.09	0.17	0.026	0.12	14.3	10.0	2.39	222	4.45	0.02	0.09
CC39562		31.7	1.45	2.39	0.05	0.10	0.18	0.021	0.05	8.2	5.2	0.44	183	2.43	0.10	0.35
CC39563		33.2	1.58	3.44	0.06	0.08	0.18	0.026	0.05	10.7	5.3	0.33	81	2.62	0.13	0.44
CC39564		32.3	1.63	4.11	0.05	0.04	0.09	0.024	0.10	11.2	6.3	0.18	61	2.84	0.06	0.50
CC39565		30.9	2.28	3.82	0.06	0.06	0.12	0.028	0.08	10.6	7.6	0.21	112	3.17	0.08	0.52
CC39566		21.4	2.15	4.38	0.05	0.03	0.07	0.024	0.07	8.8	9.7	0.22	123	2.91	0.05	0.52
CC39567		36.5	2.72	3.68	0.07	0.09	0.10	0.031	0.07	11.5	5.6	0.24	192	8.65	0.14	0.41
CC39568		36.0	1.80	4.73	<0.05	0.06	0.06	0.022	0.06	6.1	2.9	0.21	46	6.72	0.08	0.44
CC39569		23.5	1.38	2.01	0.05	0.07	0.13	0.017	0.04	8.6	2.5	0.30	79	3.51	0.11	0.23
CC39570		46.6	2.45	4.60	0.07	0.07	0.11	0.031	0.07	10.3	5.9	0.31	229	4.10	0.09	0.52
CC39571		25.5	2.69	3.74	0.05	0.06	0.05	0.027	0.09	7.4	6.7	0.24	144	5.71	0.04	0.54
CC39572		34.2	2.01	3.30	0.06	0.10	0.19	0.026	0.06	7.7	6.7	0.39	223	3.58	0.07	0.40
CC39573		30.7	1.64	1.78	<0.05	0.03	0.17	0.019	0.05	3.6	1.2	0.06	36	7.81	0.05	0.12
CC39574		50.5	4.23	2.53	0.07	0.05	0.28	0.033	0.05	5.3	2.7	0.11	148	7.31	0.06	0.25
CC39575		51.1	0.80	1.66	0.09	0.11	0.39	0.017	0.03	9.6	1.7	0.20	107	11.70	0.01	0.20
CC39576		44.6	0.69	1.34	0.09	0.11	0.42	0.015	0.03	11.6	1.7	0.14	108	12.15	0.01	0.16
CC39577		48.0	1.68	2.61	0.10	0.09	0.08	0.020	0.12	12.0	17.7	1.65	208	6.72	0.01	0.17
CC39578		66.6	1.87	3.12	0.10	0.33	0.25	0.032	0.19	13.6	6.3	1.59	168	51.10	0.08	0.12
CC39579		70.5	2.01	2.99	0.11	0.34	0.26	0.034	0.19	14.1	5.0	1.70	184	55.60	0.08	0.09
CC39580		40.4	1.63	2.45	0.09	0.11	0.06	0.020	0.12	12.0	16.1	1.61	192	4.86	0.01	0.13
CC39581		39.0	1.59	2.32	0.09	0.16	0.06	0.019	0.13	11.7	15.1	1.51	190	4.34	0.01	0.11
CC39582		43.6	1.66	2.51	0.09	0.09	0.07	0.021	0.12	12.1	17.7	1.65	195	4.42	0.01	0.15
CC39583		36.0	1.42	2.37	0.09	0.10	0.05	0.017	0.11	12.0	17.4	1.60	182	3.85	0.01	0.13
CC39584		36.1	1.47	2.73	0.10	0.08	0.06	0.018	0.11	12.0	19.8	1.69	194	3.57	0.01	0.19
CC39585		32.7	1.26	2.58	0.09	0.12	0.05	0.016	0.10	11.9	19.0	1.63	177	3.61	0.01	0.14
CC39586		55.2	1.55	2.74	0.09	0.09	0.08	0.021	0.13	12.6	18.9	1.60	190	5.79	0.01	0.16
CC39587		22.7	1.24	2.55	0.09	0.09	0.04	0.015	0.10	11.0	19.3	1.74	193	2.54	0.01	0.17
CC39588		80.9	1.05	4.60	0.12	0.13	0.23	0.017	0.20	17.0	28.6	1.54	185	2.52	0.02	0.42
CC39591		62.4	1.42	2.18	0.07	0.08	0.15	0.022	0.12	12.2	11.0	2.38	227	5.24	0.02	0.10
CC39592		52.8	1.33	2.10	0.07	0.11	0.14	0.022	0.13	12.6	10.7	2.58	231	4.64	0.02	0.08
CC39593		62.9	1.48	2.29	0.07	0.07	0.19	0.024	0.13	12.1	11.8	2.45	226	5.79	0.02	0.10

Comments: Interference: Ca>10% on ICP-MS As,ICP-AES results shown. Gold determinations by ME-MS41 are semi-quantitative due to the small sample weight used (0.5g).

ALS Chemex

EXCELLENCE IN ANALYTICAL CHEMISTRY

ALS Canada Ltd.

212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: STRATEGIC METALS LTD.
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO

Finalized Date: 27-JUL-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07077183

Sample Description	Method	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41
	Analyte	Ni	P	Pb	Rb	Re	S	Sb	Sc	Se	Sn	Sr	Ta	Te	Th	Ti
	Units	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%
	LOR	0.2	10	0.2	0.1	0.001	0.01	0.05	0.1	0.2	0.2	0.2	0.01	0.01	0.2	0.005
CC39550		51.3	640	11.1	11.3	0.005	0.08	0.64	3.5	3.8	0.4	33.2	<0.01	0.06	2.7	<0.005
CC39553		9.4	860	18.9	19.9	0.001	0.24	28.10	2.9	43.7	0.9	159.0	<0.01	0.34	3.0	0.009
CC39554		126.5	380	16.1	14.4	0.002	0.15	6.81	2.7	8.9	0.7	27.7	<0.01	0.12	2.3	<0.005
CC39555		235.0	570	11.7	6.8	0.014	0.13	10.40	3.3	16.2	0.5	109.5	0.01	0.14	1.3	<0.005
CC39556		268.0	810	7.9	6.6	0.011	0.19	8.47	2.6	15.4	0.4	157.0	0.01	0.11	0.6	<0.005
CC39557		270.0	820	8.1	6.8	0.024	0.22	8.29	2.4	17.0	0.5	175.0	0.01	0.09	0.6	<0.005
CC39558		141.0	490	6.4	5.3	0.009	0.18	9.14	2.1	7.2	0.3	167.5	0.01	0.07	0.6	<0.005
CC39559		86.8	570	8.7	8.1	0.005	0.12	6.88	3.2	4.2	0.5	109.5	<0.01	0.09	1.4	<0.005
CC39560		48.9	540	10.0	9.4	0.004	0.11	3.01	5.0	3.3	0.4	78.8	<0.01	0.07	2.3	<0.005
CC39561		26.9	1540	19.1	8.9	0.009	0.17	2.42	4.1	2.0	0.2	197.0	<0.01	0.05	3.4	<0.005
CC39562		42.4	900	6.9	5.5	0.004	0.15	1.26	4.7	3.1	0.3	176.5	<0.01	0.03	1.6	0.008
CC39563		36.5	1040	6.5	5.2	0.001	0.13	1.12	5.2	3.0	0.4	128.5	<0.01	0.04	1.7	0.008
CC39564		26.7	490	9.0	13.7	<0.001	0.04	0.75	3.7	1.7	0.5	38.3	<0.01	0.05	2.5	0.010
CC39565		34.9	400	8.4	9.7	0.001	0.05	1.13	4.3	2.2	0.5	32.6	<0.01	0.05	3.5	0.011
CC39566		25.4	420	9.3	10.0	0.001	0.05	0.97	3.2	1.4	0.5	32.8	<0.01	0.04	2.5	0.011
CC39567		36.9	500	12.1	7.0	0.001	0.04	1.21	5.4	2.9	0.5	73.0	<0.01	0.05	2.4	0.008
CC39568		36.1	220	8.8	7.0	0.001	0.04	1.18	3.2	1.5	0.7	52.6	<0.01	0.05	2.1	0.007
CC39569		34.3	840	6.3	5.3	0.001	0.13	1.16	3.3	2.5	0.3	149.5	0.01	0.03	1.3	0.006
CC39570		60.9	560	12.8	10.5	0.002	0.05	1.21	6.6	2.5	0.6	87.4	<0.01	0.05	2.4	0.009
CC39571		32.2	330	11.0	9.0	0.001	0.03	1.28	3.3	1.7	0.4	37.8	<0.01	0.04	2.9	0.013
CC39572		48.7	840	9.1	7.7	0.003	0.09	1.33	4.9	4.2	0.4	137.0	<0.01	0.05	1.5	0.008
CC39573		28.6	470	7.5	7.7	0.004	0.10	2.13	2.1	2.9	0.3	54.6	<0.01	0.05	1.0	<0.005
CC39574		70.8	440	14.9	5.9	0.002	0.07	5.13	4.7	5.3	0.5	60.3	<0.01	0.06	2.7	0.005
CC39575		146.0	710	5.9	4.1	0.010	0.18	6.58	2.6	11.7	0.3	132.0	0.01	0.08	0.7	<0.005
CC39576		160.0	700	6.0	4.8	0.011	0.18	5.78	2.4	13.4	0.3	170.0	0.01	0.08	0.5	<0.005
CC39577		31.3	1370	12.8	11.2	0.006	0.13	2.57	3.6	2.8	0.3	538.0	<0.01	0.05	3.3	<0.005
CC39578		132.5	1620	10.5	13.4	0.045	0.13	8.86	6.4	7.9	0.8	370.0	0.01	0.09	5.5	<0.005
CC39579		171.0	2050	10.5	12.8	0.046	0.13	9.85	6.6	10.1	0.9	395.0	0.01	0.10	6.0	<0.005
CC39580		28.2	1430	11.3	10.3	0.006	0.16	1.90	3.9	2.5	0.2	567.0	<0.01	0.04	3.5	<0.005
CC39581		26.1	1450	10.8	9.6	0.006	0.17	1.72	3.8	2.5	0.2	575.0	<0.01	0.04	3.6	<0.005
CC39582		27.6	1380	11.7	10.5	0.005	0.17	1.85	3.9	2.6	0.2	572.0	<0.01	0.05	3.3	<0.005
CC39583		21.1	1450	10.3	9.5	0.004	0.15	1.56	3.3	2.0	0.2	633.0	<0.01	0.04	3.3	<0.005
CC39584		22.3	1320	11.2	11.0	0.003	0.10	1.53	3.3	2.2	0.2	607.0	<0.01	0.04	2.7	0.005
CC39585		17.2	1420	10.0	9.6	0.003	0.09	1.44	3.1	1.7	0.2	725.0	<0.01	0.04	3.3	<0.005
CC39586		25.9	1480	10.9	10.6	0.005	0.10	2.05	3.5	2.6	0.3	570.0	<0.01	0.05	3.1	<0.005
CC39587		13.8	1330	9.1	9.8	0.002	0.08	1.13	3.0	1.4	0.2	775.0	<0.01	0.03	2.8	<0.005
CC39588		42.2	4800	9.5	19.5	0.007	0.10	3.19	3.1	4.9	0.4	99.6	<0.01	0.06	2.1	0.013
CC39591		30.4	1550	17.9	8.4	0.008	0.17	2.63	4.1	2.3	0.3	217.0	<0.01	0.05	3.1	<0.005
CC39592		26.4	1680	16.7	8.0	0.009	0.19	2.56	4.2	2.1	0.3	227.0	<0.01	0.05	3.1	<0.005
CC39593		30.3	1440	18.5	8.8	0.010	0.21	2.80	4.2	2.4	0.3	222.0	<0.01	0.05	3.0	<0.005

Comments: Interference: Ca>10% on ICP-MS As,ICP-AES results shown. Gold determinations by ME-MS41 are semi-quantitative due to the small sample weight used (0.5g).

ALS Chemex

EXCELLENCE IN ANALYTICAL CHEMISTRY

ALS Canada Ltd.

212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: STRATEGIC METALS LTD.
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO

Finalized Date: 27-JUL-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07077183

Method	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41
Analyte	Ti	U	V	W	Y	Zn	Zr
Units	ppm	ppm	ppm	ppm	ppm	ppm	ppm
Sample Description LOR	0.02	0.05	1	0.05	0.05	2	0.5
CC39550	0.92	1.09	31	0.07	11.35	132	0.6
CC39553	7.84	13.30	499	0.41	12.60	32	2.1
CC39554	2.62	1.86	390	0.15	9.22	374	0.8
CC39555	1.59	11.25	440	0.23	32.20	823	6.4
CC39556	2.05	16.05	350	0.18	36.10	594	7.0
CC39557	2.13	34.00	343	0.21	34.80	522	7.7
CC39558	0.52	21.70	224	0.14	29.30	872	4.0
CC39559	0.60	13.20	275	0.15	19.75	325	3.3
CC39560	0.21	5.60	109	0.08	21.00	167	1.9
CC39561	0.26	1.57	46	0.08	14.35	168	4.2
CC39562	0.11	2.84	52	0.07	14.40	77	2.6
CC39563	0.14	3.28	54	0.10	16.95	79	1.7
CC39564	0.13	1.56	56	0.10	7.80	88	0.9
CC39565	0.13	1.91	67	0.11	8.92	150	1.8
CC39566	0.12	1.17	70	0.10	5.23	112	0.9
CC39567	0.12	3.49	72	0.10	18.50	104	2.0
CC39568	0.18	1.34	88	0.10	4.84	86	1.7
CC39569	0.09	3.25	40	0.06	15.30	57	1.8
CC39570	0.15	3.48	83	0.13	14.80	95	1.6
CC39571	0.13	1.13	85	0.11	4.59	134	2.0
CC39572	0.12	3.61	61	0.08	12.95	101	2.5
CC39573	0.13	1.53	55	0.08	5.71	124	0.7
CC39574	0.20	2.40	143	0.10	10.10	358	1.6
CC39575	1.00	10.30	211	0.12	20.80	406	5.2
CC39576	1.02	41.90	209	0.11	25.20	298	5.5
CC39577	0.21	2.16	71	0.05	13.05	211	4.6
CC39578	0.46	12.25	315	0.21	24.90	502	15.8
CC39579	0.43	14.65	337	0.23	28.90	687	16.2
CC39580	0.12	1.77	50	<0.05	13.25	153	5.6
CC39581	0.09	1.63	50	<0.05	12.60	151	7.6
CC39582	0.11	1.67	49	<0.05	13.00	154	4.7
CC39583	0.10	1.52	45	<0.05	11.55	135	5.7
CC39584	0.12	1.47	46	<0.05	11.95	137	3.6
CC39585	0.09	1.41	45	<0.05	10.95	121	6.2
CC39586	0.13	1.53	56	0.06	12.45	181	5.0
CC39587	0.09	1.22	40	<0.05	10.45	99	4.6
CC39588	0.33	5.05	210	0.07	18.20	433	4.4
CC39591	0.26	1.55	56	0.08	13.05	205	4.0
CC39592	0.20	1.49	52	0.07	13.35	171	5.1
CC39593	0.26	1.62	57	0.09	12.85	203	3.7

Comments: Interference: Ca>10% on ICP-MS As,ICP-AES results shown. Gold determinations by ME-MS41 are semi-quantitative due to the small sample weight used (0.5g).

ALS Chemex

EXCELLENCE IN ANALYTICAL CHEMISTRY

ALS Canada Ltd.

212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: STRATEGIC METALS LTD.
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO

Finalized Date: 27-JUL-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07077183

Sample Description	Method	WEI-21	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41
	Analyte	Recvd Wt.	Ag	Al	As	Au	B	Ba	Be	Bi	Ca	Cd	Ce	Co	Cr	Cs
	Units	kg	ppm	%	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppm	ppm	ppm
	LOR	0.02	0.01	0.01	0.1	0.2	10	10	0.05	0.01	0.01	0.01	0.02	0.1	1	0.05
CC39594		0.28	0.43	0.49	10.7	<0.2	<10	1410	0.54	0.12	8.03	1.36	23.50	6.3	15	0.90
CC39595		0.28	0.41	0.52	10.4	<0.2	<10	1640	0.52	0.11	7.75	1.21	22.90	6.3	17	0.93
CC39596		0.36	0.41	0.53	10.6	<0.2	<10	1510	0.52	0.13	8.01	1.23	23.40	6.4	17	0.99
CC39597		0.28	0.44	0.58	11.2	<0.2	<10	1980	0.57	0.12	7.90	1.46	23.50	6.9	19	1.00
CC39598		0.34	0.46	0.57	10.9	<0.2	<10	1220	0.58	0.12	8.18	1.20	24.20	6.9	16	1.06
CC39599		0.40	0.56	0.59	11.8	<0.2	<10	1240	0.61	0.13	8.40	1.28	23.30	7.1	16	1.10
CC39600		0.24	0.51	0.59	10.9	<0.2	<10	1300	0.59	0.12	8.86	1.33	23.60	6.7	17	1.06
CC39724		0.12	0.88	0.74	15.3	<0.2	10	2360	0.50	0.20	0.92	4.33	26.20	7.0	17	0.94
CC39726		0.16	0.56	0.72	10.5	<0.2	10	2520	0.44	0.14	0.83	2.32	28.00	4.6	19	0.86
CC39727		0.18	0.19	1.77	14.4	<0.2	<10	330	0.54	0.27	0.14	0.48	10.60	17.3	31	1.24
CC39728		0.24	0.16	1.97	26.7	<0.2	<10	720	1.62	0.30	0.31	4.85	9.49	200.0	34	2.25
CC39729		0.22	0.30	1.89	21.3	<0.2	<10	1100	1.50	0.31	0.54	6.23	12.80	108.5	31	1.91
CC39730		0.18	0.30	1.91	19.0	<0.2	<10	1190	1.44	0.27	0.49	5.21	15.15	102.0	30	2.11
CC39731		0.20	0.17	1.83	19.9	<0.2	<10	900	1.31	0.26	0.24	3.55	16.15	161.5	30	1.64
CC39732		0.24	0.43	0.88	12.0	<0.2	<10	920	0.55	0.15	9.60	2.22	24.80	9.2	18	1.76
CC39733		0.24	0.42	0.87	14	<0.2	<10	860	0.59	0.14	10.35	2.23	24.00	9.0	18	1.71
CC39734		0.18	0.45	0.87	11.7	<0.2	<10	910	0.65	0.14	9.82	2.45	24.70	9.1	18	1.74
CC39735		0.14	0.40	0.80	11.7	<0.2	<10	580	0.62	0.15	9.03	2.02	27.10	8.8	15	1.64
CC39736		0.30	0.43	0.82	18	<0.2	10	970	0.62	0.13	11.10	2.42	25.60	8.5	18	1.65
CC39737		0.20	0.42	0.75	10	<0.2	<10	840	0.56	0.12	11.20	2.47	23.80	7.9	16	1.49
CC39738		0.24	0.43	0.80	16	<0.2	<10	780	0.58	0.12	11.25	2.30	24.60	7.8	16	1.60
CC39743		0.20	0.29	0.84	12.3	<0.2	<10	300	0.58	0.16	5.26	2.09	22.80	9.2	15	1.11
CC39744		0.22	0.36	0.96	12.9	<0.2	<10	290	0.64	0.17	6.40	2.41	24.50	9.8	17	1.25
CC39745		0.20	0.27	0.85	10.7	<0.2	<10	260	0.54	0.15	5.57	1.90	25.20	8.9	15	1.09
CC39746		0.14	0.40	0.97	10.1	<0.2	<10	290	0.66	0.15	7.49	2.03	25.90	8.4	16	1.30
CC39747		0.20	0.37	0.89	12.3	<0.2	<10	260	0.60	0.17	6.03	2.48	25.10	9.3	17	1.13
CC39748		0.22	0.36	0.87	10.4	<0.2	<10	270	0.64	0.15	6.29	2.25	25.00	8.5	15	1.14
CC39749		0.18	0.30	0.81	11.2	<0.2	<10	270	0.56	0.16	6.00	2.21	25.30	8.5	15	1.01
CC39750		0.14	0.34	0.89	11.5	<0.2	<10	250	0.62	0.17	4.89	2.18	26.20	9.2	16	1.15
CC39751		0.12	0.34	0.95	14.6	<0.2	<10	400	0.64	0.18	5.80	2.83	26.40	9.7	23	1.19
CC39752		0.18	0.32	0.98	11.3	<0.2	<10	240	0.64	0.19	3.68	1.79	33.80	9.1	17	1.19
CC39753		0.12	0.37	0.88	11.0	<0.2	<10	280	0.65	0.15	8.27	2.63	26.90	8.5	15	1.10
CC39754		0.16	0.40	0.89	13.4	<0.2	<10	280	0.60	0.15	7.91	2.91	27.30	8.2	16	1.19
CC39755		0.20	0.40	0.87	12.3	<0.2	<10	300	0.67	0.16	7.46	3.08	29.00	8.5	16	1.08
CC39756		0.24	0.42	0.85	12.1	<0.2	<10	290	0.61	0.15	7.86	3.31	27.10	8.5	16	1.14
CC39757		0.28	0.43	0.86	13.3	<0.2	<10	270	0.60	0.15	7.57	3.58	26.40	8.8	19	1.11
CC39758		0.24	0.24	0.81	8.7	<0.2	<10	190	0.56	0.14	8.52	1.15	28.50	8.1	14	1.05
CC39759		0.16	0.25	0.83	8.2	<0.2	<10	180	0.53	0.13	8.69	1.11	24.30	7.9	14	1.00
CC39760		0.16	0.27	0.87	9.4	<0.2	<10	210	0.58	0.15	9.19	1.29	26.50	8.9	14	1.11
CC39761		0.14	0.30	0.93	9.0	<0.2	<10	210	0.63	0.16	8.49	1.25	25.70	8.7	15	1.24

Comments: Interference: Ca>10% on ICP-MS As,ICP-AES results shown. Gold determinations by ME-MS41 are semi-quantitative due to the small sample weight used (0.5g).

ALS Chemex

EXCELLENCE IN ANALYTICAL CHEMISTRY

ALS Canada Ltd.

212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: STRATEGIC METALS LTD.
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO

Finalized Date: 27-JUL-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07077183

Sample Description	Method	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41
	Analyte	Cu	Fe	Ga	Ge	Hf	Hg	In	K	La	Li	Mg	Mn	Mo	Na	Nb
	Units	ppm	%	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	%	ppm	ppm	%	ppm
	LOR	0.2	0.01	0.05	0.05	0.02	0.01	0.005	0.01	0.2	0.1	0.01	5	0.05	0.01	0.05
CC39594		54.3	1.33	1.99	0.08	0.08	0.15	0.023	0.11	12.4	10.2	2.42	219	5.52	0.02	0.10
CC39595		55.0	1.32	2.09	0.07	0.11	0.17	0.022	0.13	12.2	10.1	2.26	220	5.67	0.02	0.08
CC39596		57.2	1.39	2.14	0.07	0.10	0.16	0.023	0.13	12.4	10.8	2.45	224	5.40	0.02	0.08
CC39597		56.2	1.44	2.29	0.08	0.09	0.16	0.023	0.14	12.4	10.9	2.37	224	7.73	0.03	0.09
CC39598		57.4	1.37	2.35	0.08	0.08	0.19	0.022	0.13	13.0	12.8	2.28	226	4.75	0.02	0.09
CC39599		67.0	1.53	2.38	0.08	0.07	0.21	0.025	0.12	12.5	13.3	2.34	225	5.07	0.02	0.11
CC39600		63.4	1.46	2.30	0.07	0.08	0.22	0.024	0.13	12.7	12.7	2.45	238	4.92	0.02	0.10
CC39724		45.2	1.75	2.65	0.07	0.06	0.25	0.028	0.09	12.8	7.5	0.20	204	10.75	0.04	0.21
CC39726		37.6	1.29	2.95	0.06	0.05	0.19	0.022	0.11	14.2	7.1	0.19	116	6.34	0.04	0.17
CC39727		27.8	3.54	5.61	0.05	0.04	0.07	0.040	0.10	5.4	21.5	0.39	379	3.92	0.01	0.24
CC39728		59.9	7.00	5.71	0.09	0.09	0.06	0.061	0.10	4.1	25.1	0.58	4680	8.96	0.02	0.10
CC39729		58.9	5.69	5.49	0.08	0.06	0.11	0.054	0.11	6.0	23.4	0.44	2880	7.22	0.02	0.15
CC39730		58.2	5.59	5.10	0.09	0.09	0.11	0.048	0.10	6.1	22.7	0.45	2820	7.52	0.02	0.15
CC39731		51.0	4.21	5.18	0.08	0.11	0.08	0.051	0.10	6.9	23.8	0.47	4350	7.23	0.02	0.11
CC39732		43.3	1.97	2.87	0.07	0.15	0.06	0.026	0.14	13.8	15.3	1.51	241	8.59	0.02	0.12
CC39733		43.8	1.92	2.79	0.07	0.13	0.07	0.025	0.13	13.3	17.2	1.61	230	8.05	0.02	0.12
CC39734		41.5	1.91	2.78	0.07	0.12	0.07	0.025	0.13	13.8	18.0	1.53	229	8.77	0.02	0.14
CC39735		38.5	1.90	2.57	0.07	0.11	0.06	0.022	0.12	14.7	19.4	1.37	235	6.46	0.02	0.12
CC39736		40.9	1.80	2.68	0.06	0.17	0.08	0.022	0.15	14.3	16.5	1.67	222	8.74	0.02	0.11
CC39737		40.2	1.71	2.44	0.07	0.15	0.08	0.022	0.13	13.4	16.7	1.62	206	8.18	0.02	0.12
CC39738		37.7	1.71	2.59	0.06	0.12	0.07	0.022	0.14	13.8	18.4	1.67	211	7.30	0.02	0.12
CC39743		28.1	2.10	2.50	0.06	0.09	0.05	0.023	0.07	12.2	23.1	0.83	208	5.77	0.01	0.09
CC39744		32.9	2.23	2.86	0.06	0.09	0.07	0.025	0.08	13.0	25.6	1.03	216	6.11	0.01	0.11
CC39745		25.7	2.06	2.44	0.06	0.10	0.05	0.022	0.07	13.6	24.6	0.92	178	4.93	0.01	0.09
CC39746		32.2	1.94	2.95	0.07	0.10	0.06	0.023	0.09	14.3	26.8	1.29	242	4.35	0.01	0.15
CC39747		30.4	2.17	2.58	0.07	0.09	0.06	0.024	0.07	13.5	24.8	0.99	209	6.32	0.01	0.10
CC39748		30.8	1.95	2.60	0.07	0.10	0.06	0.022	0.08	13.7	26.3	1.09	200	4.89	0.01	0.12
CC39749		27.1	2.00	2.42	0.07	0.09	0.05	0.023	0.07	13.4	24.2	0.94	191	5.40	0.01	0.09
CC39750		31.7	2.17	2.65	0.06	0.09	0.05	0.024	0.07	14.1	27.4	0.95	175	5.49	0.01	0.10
CC39751		31.8	2.34	2.78	0.06	0.11	0.06	0.027	0.08	14.2	25.9	0.94	209	8.31	0.01	0.09
CC39752		28.2	2.28	2.89	0.06	0.10	0.05	0.023	0.08	18.1	29.6	0.96	151	4.84	0.01	0.10
CC39753		29.3	1.93	2.64	0.06	0.10	0.06	0.021	0.08	14.5	25.7	1.31	213	5.37	0.01	0.13
CC39754		28.7	1.94	2.69	0.09	0.09	0.08	0.024	0.09	14.2	23.2	1.26	203	6.53	0.01	0.12
CC39755		29.0	2.02	2.55	0.06	0.09	0.07	0.021	0.08	15.8	24.3	1.16	205	6.44	0.01	0.11
CC39756		29.2	1.92	2.57	0.06	0.09	0.08	0.023	0.08	14.7	24.6	1.21	202	6.38	0.01	0.12
CC39757		30.3	1.97	2.56	0.06	0.09	0.08	0.022	0.08	14.5	23.9	1.20	213	7.63	0.01	0.12
CC39758		23.8	1.85	2.45	0.08	0.09	0.03	0.020	0.07	15.2	24.8	1.20	205	3.39	0.01	0.11
CC39759		24.4	1.78	2.44	0.06	0.09	0.04	0.020	0.08	13.1	24.2	1.26	204	3.32	0.01	0.12
CC39760		27.1	2.00	2.53	0.07	0.11	0.04	0.022	0.08	14.4	25.8	1.29	229	3.76	0.01	0.13
CC39761		27.8	1.97	2.76	0.06	0.09	0.05	0.022	0.09	13.9	27.2	1.32	215	3.48	0.01	0.13

Comments: Interference: Ca>10% on ICP-MS As,ICP-AES results shown. Gold determinations by ME-MS41 are semi-quantitative due to the small sample weight used (0.5g).

ALS Chemex

EXCELLENCE IN ANALYTICAL CHEMISTRY

ALS Canada Ltd.

212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: STRATEGIC METALS LTD.
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO

Finalized Date: 27-JUL-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07077183

Sample Description	Method	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41
	Analyte	Ni	P	Pb	Rb	Re	S	Sb	Sc	Se	Sn	Sr	Ta	Te	Th	Ti
	Units	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%
	LOR	0.2	10	0.2	0.1	0.001	0.01	0.05	0.1	0.2	0.2	0.2	0.01	0.01	0.2	0.005
CC39594		29.6	1620	18.7	7.6	0.009	0.18	2.62	4.2	2.4	0.3	227.0	<0.01	0.05	3.0	<0.005
CC39595		29.7	1640	16.6	8.0	0.010	0.16	2.63	4.2	2.1	0.3	211.0	<0.01	0.05	3.2	<0.005
CC39596		29.9	1610	16.7	8.3	0.009	0.19	2.72	4.3	2.4	0.3	225.0	<0.01	0.05	3.1	<0.005
CC39597		36.4	1570	16.7	9.0	0.010	0.18	2.90	4.4	2.6	0.3	235.0	<0.01	0.05	3.3	<0.005
CC39598		28.4	1500	18.8	8.8	0.009	0.16	2.58	4.3	2.0	0.3	201.0	<0.01	0.05	3.1	<0.005
CC39599		31.6	1350	20.8	8.8	0.010	0.20	2.75	4.4	2.5	0.3	208.0	<0.01	0.05	3.0	<0.005
CC39600		28.7	1490	20.0	8.6	0.009	0.21	2.67	4.4	2.2	0.3	220.0	<0.01	0.06	3.0	<0.005
CC39724		43.2	620	12.5	10.1	0.020	0.19	3.44	4.2	8.4	0.4	99.2	<0.01	0.09	2.4	0.005
CC39726		33.0	750	9.5	10.4	0.021	0.16	2.26	4.0	5.1	0.4	83.4	<0.01	0.08	2.7	0.005
CC39727		41.8	540	15.9	13.7	0.001	0.05	0.85	4.7	2.2	0.6	19.0	<0.01	0.05	2.4	<0.005
CC39728		168.5	570	19.9	12.9	0.008	0.19	1.37	7.1	3.8	0.6	46.9	0.01	0.09	3.5	<0.005
CC39729		143.0	580	17.8	14.2	0.006	0.14	1.32	7.1	4.3	0.6	53.0	0.01	0.08	3.0	<0.005
CC39730		155.0	550	16.0	14.4	0.006	0.17	1.29	6.9	4.7	0.5	56.3	0.01	0.07	3.1	<0.005
CC39731		208.0	540	17.2	12.6	0.007	0.17	1.32	5.9	3.7	0.6	44.7	0.01	0.08	3.2	<0.005
CC39732		40.8	1460	13.2	11.5	0.009	0.13	2.37	4.0	2.7	0.3	469.0	0.01	0.05	4.6	<0.005
CC39733		40.1	1430	12.8	11.4	0.007	0.14	2.34	4.0	2.5	0.3	508.0	<0.01	0.05	4.2	<0.005
CC39734		41.9	1410	12.8	11.6	0.007	0.14	2.55	3.8	2.7	0.3	478.0	<0.01	0.05	4.1	<0.005
CC39735		34.1	1320	14.1	10.0	0.003	0.09	2.23	3.5	2.2	0.2	417.0	<0.01	0.04	4.3	<0.005
CC39736		40.6	1530	12.0	11.5	0.009	0.16	2.52	3.8	2.7	0.3	540.0	<0.01	0.05	4.4	<0.005
CC39737		36.8	1470	11.7	10.3	0.008	0.16	2.71	3.6	2.5	0.3	552.0	<0.01	0.04	4.1	<0.005
CC39738		33.9	1410	12.3	11.0	0.006	0.13	2.34	3.5	2.3	0.3	544.0	<0.01	0.04	4.0	<0.005
CC39743		33.9	830	14.6	6.9	0.005	0.07	2.14	3.0	2.0	0.2	302.0	<0.01	0.04	3.9	<0.005
CC39744		35.7	940	15.5	8.4	0.005	0.08	2.22	3.4	2.4	0.2	355.0	<0.01	0.04	4.0	<0.005
CC39745		30.2	830	14.0	6.8	0.003	0.06	1.83	2.8	1.7	0.2	308.0	<0.01	0.03	4.1	<0.005
CC39746		29.4	1090	13.7	9.7	0.003	0.08	1.76	3.4	2.1	0.2	398.0	<0.01	0.04	3.2	<0.005
CC39747		35.2	900	15.9	7.5	0.005	0.07	2.40	3.1	2.3	0.2	338.0	<0.01	0.04	4.0	<0.005
CC39748		30.1	950	14.4	7.7	0.003	0.07	1.96	3.0	2.2	0.2	352.0	<0.01	0.03	3.4	<0.005
CC39749		31.0	900	14.5	6.7	0.004	0.07	2.07	2.8	2.1	0.2	337.0	<0.01	0.03	3.9	<0.005
CC39750		32.1	880	16.0	7.3	0.003	0.06	2.04	3.1	2.1	0.2	271.0	<0.01	0.03	4.1	<0.005
CC39751		43.0	880	16.5	7.7	0.007	0.08	2.86	3.3	2.5	0.3	337.0	<0.01	0.04	4.6	<0.005
CC39752		29.9	870	17.5	7.7	0.002	0.05	1.78	3.1	1.8	0.2	206.0	<0.01	0.03	4.8	<0.005
CC39753		30.0	1040	14.3	8.4	0.003	0.07	2.15	3.0	2.2	0.2	458.0	<0.01	0.03	3.7	<0.005
CC39754		33.5	1020	15.7	8.3	0.005	0.06	2.54	2.9	2.4	0.2	459.0	<0.01	0.05	4.1	<0.005
CC39755		33.0	990	14.6	7.6	0.005	0.07	2.66	2.9	2.5	0.2	415.0	<0.01	0.04	4.0	<0.005
CC39756		32.8	1000	14.0	8.1	0.005	0.07	2.67	3.0	2.6	0.2	435.0	<0.01	0.04	3.9	<0.005
CC39757		37.2	950	14.6	7.9	0.006	0.07	3.03	3.0	2.8	0.2	432.0	<0.01	0.04	3.8	<0.005
CC39758		22.5	1010	13.6	7.4	0.001	0.05	1.28	2.7	1.3	0.2	478.0	<0.01	0.03	3.8	<0.005
CC39759		22.3	970	13.1	7.7	0.001	0.05	1.21	2.7	1.3	0.2	495.0	<0.01	0.02	3.5	<0.005
CC39760		25.1	1020	15.2	8.0	0.001	0.06	1.44	2.9	1.5	0.2	507.0	<0.01	0.03	4.0	<0.005
CC39761		24.6	1010	15.4	8.8	0.001	0.07	1.33	3.0	1.6	0.2	474.0	<0.01	0.03	3.8	<0.005

Comments: Interference: Ca>10% on ICP-MS As,ICP-AES results shown. Gold determinations by ME-MS41 are semi-quantitative due to the small sample weight used (0.5g).

ALS Chemex

EXCELLENCE IN ANALYTICAL CHEMISTRY

ALS Canada Ltd.

212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: STRATEGIC METALS LTD.
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO

Finalized Date: 27-JUL-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07077183

Sample Description	Method	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41
	Analyte	Tl	U	V	W	Y	Zn	Zr
	Units	ppm	ppm	ppm	ppm	ppm	ppm	ppm
	LOR	0.02	0.05	1	0.05	0.05	2	0.5
CC39594		0.23	1.66	53	0.08	13.55	193	4.3
CC39595		0.23	1.73	60	0.08	13.05	192	5.4
CC39596		0.22	1.69	57	0.08	13.35	186	4.9
CC39597		0.27	2.19	77	0.09	14.10	212	4.7
CC39598		0.24	1.48	51	0.08	13.15	180	4.4
CC39599		0.26	1.40	48	0.08	13.05	196	3.6
CC39600		0.27	1.41	49	0.10	13.00	199	3.9
CC39724		1.04	4.12	93	0.12	13.45	278	1.8
CC39726		0.84	2.72	128	0.09	12.30	295	1.7
CC39727		0.31	0.67	65	0.08	5.30	131	0.7
CC39728		0.61	1.62	62	<0.05	12.55	662	2.5
CC39729		0.64	1.99	70	0.06	16.25	590	1.2
CC39730		0.65	2.00	67	0.06	27.20	628	1.4
CC39731		0.53	1.42	67	0.06	30.70	518	2.0
CC39732		0.21	2.63	88	0.05	15.15	233	6.7
CC39733		0.21	2.47	85	0.05	14.60	231	6.0
CC39734		0.23	2.48	87	0.05	14.50	263	5.3
CC39735		0.20	1.84	66	0.07	13.45	208	5.3
CC39736		0.19	2.65	96	0.06	15.20	243	7.6
CC39737		0.17	2.42	79	0.05	14.65	240	6.8
CC39738		0.19	2.19	79	0.05	13.95	225	6.3
CC39743		0.18	1.44	58	<0.05	10.55	212	3.7
CC39744		0.20	1.57	62	<0.05	12.15	232	3.5
CC39745		0.15	1.24	46	<0.05	10.50	194	3.7
CC39746		0.18	1.38	53	0.05	12.75	193	3.2
CC39747		0.19	1.54	60	<0.05	11.85	235	3.4
CC39748		0.18	1.37	48	<0.05	11.90	203	3.2
CC39749		0.16	1.37	51	<0.05	10.95	214	3.4
CC39750		0.17	1.28	49	<0.05	11.75	212	3.4
CC39751		0.22	1.72	77	0.05	11.90	270	4.5
CC39752		0.15	1.16	46	<0.05	12.20	187	3.3
CC39753		0.18	1.43	55	0.05	12.55	241	3.4
CC39754		0.20	1.45	65	0.06	11.65	260	3.6
CC39755		0.20	1.55	66	<0.05	12.35	272	3.5
CC39756		0.20	1.52	66	0.05	12.30	283	3.5
CC39757		0.21	1.63	73	0.05	12.55	307	3.6
CC39758		0.10	1.12	30	<0.05	11.15	121	3.8
CC39759		0.10	1.13	32	<0.05	11.00	119	3.4
CC39760		0.10	1.24	34	<0.05	12.00	133	4.1
CC39761		0.11	1.22	33	<0.05	12.40	131	3.4

Comments: Interference: Ca>10% on ICP-MS As,ICP-AES results shown. Gold determinations by ME-MS41 are semi-quantitative due to the small sample weight used (0.5g).

ALS Chemex

EXCELLENCE IN ANALYTICAL CHEMISTRY

ALS Canada Ltd.

212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: STRATEGIC METALS LTD.
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO

Finalized Date: 27-JUL-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07077183

Sample Description	Method	WEI-21	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41
	Analyte	Recvd Wt.	Ag	Al	As	Au	B	Ba	Be	Bi	Ca	Cd	Ce	Co	Cr	Cs
	Units	kg	ppm	%	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppm	ppm	ppm
	LOR	0.02	0.01	0.01	0.1	0.2	10	10	0.05	0.01	0.01	0.01	0.02	0.1	1	0.05
CC39762		0.22	0.29	0.88	9.0	<0.2	<10	210	0.58	0.15	8.90	1.27	25.50	8.5	14	1.18
CC39763		0.10	0.28	0.92	8.7	<0.2	<10	210	0.63	0.14	9.91	1.16	26.40	8.4	14	1.22
CC39764		0.22	0.19	0.78	8.7	<0.2	<10	190	0.50	0.14	8.44	1.17	33.30	8.4	13	0.96
CC39765		0.26	0.26	0.91	8.7	<0.2	<10	200	0.63	0.14	9.87	1.09	25.50	8.1	14	1.16
CC39766		0.16	0.23	0.85	9.0	<0.2	<10	200	0.55	0.15	9.57	1.11	25.10	8.7	15	1.13
CC39784		0.24	0.43	1.21	9.8	<0.2	10	720	0.85	0.16	3.39	1.65	38.80	8.6	25	0.92
CC39785		0.10	0.66	1.08	8.2	<0.2	10	1070	0.83	0.14	3.50	2.29	35.30	7.8	23	1.15
CC39786		0.14	0.56	1.06	9.3	<0.2	10	1070	0.89	0.15	3.69	2.07	37.20	7.7	24	1.09
CC39787		0.22	0.53	1.06	8.8	<0.2	10	1870	0.80	0.14	3.83	1.72	36.70	7.3	23	1.01
CC39788		0.24	0.68	1.01	11.9	<0.2	10	2400	0.77	0.15	3.63	3.06	35.90	7.8	24	1.08
CC39789		0.36	0.63	0.78	16.8	<0.2	10	3050	0.66	0.17	3.32	5.02	34.00	9.1	22	1.06
CC39790		0.14	0.52	0.72	18.6	<0.2	10	2340	0.74	0.15	2.81	6.27	30.90	7.5	21	0.94
CC39791		0.14	0.59	0.74	20.8	<0.2	10	2770	0.62	0.17	2.86	5.29	31.10	8.7	25	0.95
CC39792		0.16	0.63	0.71	19.9	<0.2	<10	2440	0.63	0.16	2.91	5.99	28.90	8.2	22	0.92
CC39793		0.24	0.61	0.71	19.2	<0.2	10	2020	0.67	0.15	2.76	4.80	26.90	6.6	21	0.94
CC39794		0.36	0.62	0.66	25.7	<0.2	10	2290	0.71	0.19	2.31	4.98	26.60	8.2	24	0.98
CC39795		0.34	0.61	0.63	28.5	<0.2	10	1850	0.67	0.18	2.04	5.11	23.60	7.7	21	0.96
CC39796		0.26	0.58	0.74	22.3	<0.2	10	1560	0.65	0.16	2.23	5.53	23.50	8.9	21	1.08
CC39797		0.28	0.51	0.79	22.4	<0.2	<10	1750	0.66	0.18	1.96	6.80	23.90	18.9	21	1.15
CC39798		0.26	0.55	0.87	29.3	<0.2	10	1670	0.76	0.21	1.57	7.52	21.40	18.1	23	1.23
CC39601		0.16	0.56	0.11	14.4	<0.2	10	440	0.13	0.14	0.05	0.17	3.39	1.1	5	0.83
CC39602		0.28	0.43	0.16	25.4	<0.2	<10	360	0.23	0.19	0.06	0.27	4.87	3.1	8	0.86
CC39603		0.22	0.29	0.21	16.7	<0.2	<10	610	0.16	0.13	0.03	0.20	4.61	1.6	10	0.61
CC39604		0.16	0.48	0.18	31.0	<0.2	<10	450	0.27	0.15	0.06	1.17	4.38	3.1	11	0.79
CC39606		0.24	0.50	0.31	49.0	<0.2	<10	260	0.33	0.15	0.01	0.83	4.78	0.9	38	1.10
CC39607		0.08	0.58	0.42	63.2	<0.2	<10	150	0.21	0.14	0.02	0.57	4.21	1.1	62	1.04
CC39608		0.12	0.58	0.29	48.2	<0.2	<10	310	0.20	0.15	0.02	0.55	4.41	1.2	36	1.12
CC39609		0.12	0.58	0.28	41.5	<0.2	<10	300	0.22	0.15	0.01	0.75	5.19	1.2	31	1.24
CC39610		0.14	0.64	0.39	38.5	<0.2	<10	480	0.26	0.18	0.02	0.70	7.45	2.7	24	1.47
CC39611		0.20	0.62	0.52	60.6	<0.2	<10	400	0.23	0.16	0.02	0.62	5.68	1.5	35	1.27
CC39612		0.16	0.56	0.30	40.1	<0.2	<10	380	0.21	0.16	0.02	0.55	5.78	1.5	27	1.30
CC39613		0.18	0.64	0.43	52.2	<0.2	<10	310	0.34	0.17	0.02	1.63	6.11	2.1	26	1.17
CC39614		0.12	0.65	0.39	50.4	<0.2	<10	320	0.26	0.15	0.02	0.85	5.37	2.1	40	1.25
CC39615		0.28	0.60	0.45	45.7	<0.2	<10	400	0.39	0.17	0.02	1.38	6.07	1.9	26	1.16
CC39616		0.20	0.71	0.79	70.7	<0.2	<10	140	0.59	0.22	0.04	2.47	6.74	3.8	28	1.21
CC39617		0.22	0.70	0.78	55.6	<0.2	<10	280	0.58	0.18	0.05	2.91	6.54	3.0	26	1.15
CC39618		0.18	0.55	0.51	38.1	<0.2	<10	380	0.33	0.15	0.02	1.25	5.97	2.0	23	1.18
CC39619		0.20	0.77	0.94	42.7	<0.2	<10	480	0.58	0.16	0.12	5.18	6.65	3.4	30	1.24
CC39632		0.18	0.68	0.98	20.7	<0.2	10	4940	0.87	0.14	6.34	9.95	26.80	8.6	34	1.43
CC39633		0.20	0.83	0.83	25.6	<0.2	10	5850	0.72	0.18	3.82	20.40	27.10	10.9	33	1.23

Comments: Interference: Ca>10% on ICP-MS As,ICP-AES results shown. Gold determinations by ME-MS41 are semi-quantitative due to the small sample weight used (0.5g).

ALS Chemex
EXCELLENCE IN ANALYTICAL CHEMISTRY
ALS Canada Ltd.
212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: STRATEGIC METALS LTD.
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO

Finalized Date: 27-JUL-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07077183

Sample Description	Method	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41
	Analyte	Cu	Fe	Ga	Ge	Hf	Hg	In	K	La	Li	Mg	Mn	Mo	Na	Nb
	Units	ppm	%	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	%	ppm	ppm	%	ppm
	LOR	0.2	0.01	0.05	0.05	0.02	0.01	0.005	0.01	0.2	0.1	0.01	5	0.05	0.01	0.05
CC39762		26.0	1.92	2.59	0.06	0.09	0.04	0.022	0.08	13.9	25.8	1.31	215	3.45	0.01	0.13
CC39763		25.5	1.88	2.71	0.06	0.09	0.04	0.021	0.09	14.4	26.6	1.46	226	3.31	0.01	0.14
CC39764		21.1	1.92	2.27	0.06	0.11	0.02	0.020	0.07	17.8	23.7	1.04	196	3.28	0.01	0.09
CC39765		25.7	1.79	2.66	0.06	0.09	0.04	0.021	0.10	14.0	26.0	1.45	213	3.24	0.01	0.14
CC39766		24.0	1.93	2.47	0.06	0.10	0.05	0.022	0.08	13.5	25.3	1.26	226	3.54	0.01	0.11
CC39784		38.3	2.05	4.04	0.08	0.12	0.08	0.029	0.19	21.5	19.6	2.10	220	4.64	0.02	0.22
CC39785		52.7	1.65	3.71	0.08	0.11	0.13	0.027	0.20	20.4	20.0	2.04	234	3.33	0.02	0.25
CC39786		45.7	1.79	3.61	0.08	0.12	0.11	0.030	0.20	21.4	19.4	2.15	238	4.29	0.02	0.22
CC39787		42.3	1.81	3.62	0.08	0.11	0.10	0.027	0.20	21.2	17.8	2.24	220	4.26	0.03	0.19
CC39788		46.8	2.10	3.37	0.09	0.11	0.12	0.031	0.19	20.8	16.0	2.14	182	6.91	0.04	0.18
CC39789		53.9	2.21	2.58	0.08	0.11	0.13	0.033	0.16	19.9	9.7	1.76	247	19.15	0.06	0.12
CC39790		53.3	1.98	2.63	0.09	0.10	0.10	0.030	0.15	18.1	9.2	1.42	222	20.60	0.04	0.13
CC39791		63.0	2.20	2.60	0.10	0.12	0.11	0.035	0.16	18.0	8.3	1.47	257	23.60	0.05	0.12
CC39792		66.2	2.11	2.45	0.09	0.10	0.12	0.032	0.14	17.0	9.0	1.49	238	21.70	0.05	0.13
CC39793		61.3	1.84	2.59	0.08	0.08	0.12	0.030	0.15	15.8	8.8	1.42	183	17.90	0.04	0.12
CC39794		70.8	2.05	2.71	0.09	0.10	0.12	0.035	0.15	15.6	6.9	1.10	215	22.60	0.04	0.11
CC39795		72.1	2.07	2.57	0.09	0.11	0.11	0.038	0.15	13.7	6.2	0.96	196	22.60	0.03	0.10
CC39796		62.7	2.20	2.57	0.08	0.08	0.11	0.034	0.14	13.7	8.5	1.17	206	16.85	0.03	0.12
CC39797		64.7	2.42	2.65	0.07	0.08	0.10	0.034	0.14	13.9	8.9	0.98	412	16.75	0.03	0.10
CC39798		66.6	2.71	2.69	0.08	0.11	0.09	0.041	0.12	12.2	9.1	0.82	384	19.80	0.03	0.09
CC39601		25.7	1.40	0.93	0.05	0.10	0.32	0.024	0.20	1.7	0.5	0.02	89	40.70	0.01	<0.05
CC39602		36.8	1.87	1.80	0.06	0.09	0.46	0.029	0.24	2.3	1.1	0.02	244	40.90	0.01	0.05
CC39603		39.4	1.59	1.35	<0.05	0.02	0.42	0.018	0.14	2.2	1.2	0.03	41	21.40	0.01	<0.05
CC39604		51.5	1.72	1.59	0.06	0.11	0.26	0.027	0.20	2.1	1.2	0.03	187	41.60	0.01	0.05
CC39606		74.0	4.84	4.08	0.10	0.05	0.35	0.067	0.16	2.2	1.5	0.02	35	57.60	<0.01	0.08
CC39607		73.2	9.88	5.32	0.17	0.05	0.31	0.101	0.15	1.8	1.1	0.02	49	77.60	<0.01	0.10
CC39608		68.3	6.12	3.58	0.12	0.06	0.35	0.060	0.17	2.0	1.2	0.02	57	67.60	0.01	0.08
CC39609		72.6	5.52	3.37	0.11	0.05	0.36	0.064	0.16	2.4	1.4	0.02	53	64.60	0.01	0.08
CC39610		73.5	3.77	3.16	0.09	0.03	0.46	0.051	0.17	3.5	3.0	0.05	121	62.30	0.01	0.10
CC39611		73.6	4.63	3.38	0.13	0.07	0.39	0.066	0.17	2.8	1.7	0.03	60	79.10	0.01	0.09
CC39612		66.7	4.28	3.32	0.10	0.04	0.39	0.051	0.16	2.8	1.8	0.03	62	57.50	0.01	0.09
CC39613		99.9	3.72	3.06	0.11	0.09	0.39	0.053	0.20	2.9	1.6	0.02	72	73.20	0.01	0.11
CC39614		80.6	5.92	3.91	0.13	0.05	0.41	0.071	0.15	2.4	1.9	0.03	88	74.10	0.01	0.11
CC39615		108.0	3.41	2.85	0.11	0.09	0.41	0.054	0.17	2.9	1.4	0.02	69	67.00	0.01	0.10
CC39616		141.0	4.27	3.56	0.15	0.15	0.37	0.069	0.32	3.0	2.9	0.04	114	95.20	0.01	0.14
CC39617		145.5	3.40	3.14	0.12	0.11	0.38	0.058	0.22	3.1	1.9	0.03	89	76.90	0.01	0.14
CC39618		97.8	3.19	2.73	0.10	0.05	0.36	0.046	0.16	2.8	2.0	0.03	74	57.70	0.01	0.10
CC39619		146.5	3.16	2.93	0.10	0.07	0.41	0.046	0.16	3.3	2.6	0.05	98	62.10	0.01	0.24
CC39632		60.1	1.94	3.48	0.09	0.11	0.18	0.028	0.20	15.4	10.6	1.97	242	32.20	0.09	0.28
CC39633		69.4	2.22	2.99	0.09	0.11	0.24	0.032	0.18	15.3	6.3	1.68	244	42.30	0.10	0.23

Comments: Interference: Ca>10% on ICP-MS As,ICP-AES results shown. Gold determinations by ME-MS41 are semi-quantitative due to the small sample weight used (0.5g).

ALS Chemex

EXCELLENCE IN ANALYTICAL CHEMISTRY

ALS Canada Ltd.

212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: STRATEGIC METALS LTD.
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO

Finalized Date: 27-JUL-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07077183

Sample Description	Method	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41
	Analyte	Ni	P	Pb	Rb	Re	S	Sb	Sc	Se	Sn	Sr	Ta	Te	Th	Ti
	Units	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%
	LOR	0.2	10	0.2	0.1	0.001	0.01	0.05	0.1	0.2	0.2	0.2	0.01	0.01	0.2	0.005
CC39762		23.6	990	14.3	8.3	0.001	0.06	1.30	2.9	1.6	0.2	500.0	<0.01	0.03	3.7	<0.005
CC39763		23.3	1070	13.9	9.3	<0.001	0.07	1.22	3.0	1.4	0.2	568.0	<0.01	0.03	3.6	<0.005
CC39764		22.1	990	13.9	6.0	<0.001	0.05	1.13	2.5	1.1	0.2	462.0	<0.01	0.03	4.5	<0.005
CC39765		21.8	1130	13.6	8.9	<0.001	0.07	1.20	3.0	1.4	0.2	600.0	<0.01	0.03	3.5	<0.005
CC39766		23.3	1060	14.5	8.0	<0.001	0.06	1.20	2.7	1.3	0.2	546.0	<0.01	0.03	4.0	<0.005
CC39784		39.4	2860	43.0	14.9	0.003	0.06	2.33	3.2	2.2	0.4	54.2	<0.01	0.07	3.8	0.006
CC39785		39.3	3330	34.5	15.2	0.004	0.09	2.04	3.5	2.7	0.4	60.8	<0.01	0.06	2.9	0.008
CC39786		39.5	3060	40.0	14.9	0.005	0.11	2.53	3.5	2.6	0.4	67.2	<0.01	0.07	3.3	0.006
CC39787		37.3	2990	30.7	14.5	0.007	0.12	2.26	3.6	2.5	0.3	76.8	<0.01	0.07	3.7	0.005
CC39788		53.0	2440	30.1	13.7	0.013	0.14	2.95	4.0	3.2	0.3	102.5	<0.01	0.07	3.7	0.005
CC39789		82.6	1500	21.6	11.0	0.027	0.14	3.66	4.5	4.0	0.4	146.0	<0.01	0.09	4.1	<0.005
CC39790		80.2	1860	22.2	11.6	0.021	0.11	4.82	3.7	4.7	0.4	122.5	<0.01	0.09	3.5	<0.005
CC39791		79.8	1670	20.6	10.9	0.028	0.14	5.37	4.2	5.1	0.4	149.0	<0.01	0.11	4.0	<0.005
CC39792		80.0	1660	21.5	10.4	0.025	0.14	5.09	4.1	5.2	0.4	141.5	<0.01	0.10	3.5	<0.005
CC39793		64.1	1690	20.3	11.0	0.025	0.15	4.24	3.9	5.4	0.4	124.5	<0.01	0.10	3.0	<0.005
CC39794		72.0	1360	20.1	10.8	0.034	0.18	5.16	4.6	6.9	0.5	137.5	<0.01	0.13	3.5	<0.005
CC39795		67.4	1270	19.6	10.5	0.035	0.22	4.86	4.6	7.1	0.5	123.5	<0.01	0.12	3.3	<0.005
CC39796		64.3	1410	19.6	10.7	0.023	0.22	4.18	4.2	6.3	0.4	100.5	<0.01	0.11	3.0	<0.005
CC39797		69.0	1500	19.6	10.8	0.024	0.21	3.97	4.3	5.5	0.4	102.0	<0.01	0.11	3.4	<0.005
CC39798		79.5	1080	20.5	10.2	0.030	0.22	4.66	5.3	6.3	0.5	107.0	<0.01	0.12	3.7	<0.005
CC39601		4.5	110	9.5	10.4	0.028	0.56	3.25	0.9	6.7	0.4	24.6	<0.01	0.08	1.6	<0.005
CC39602		7.9	190	10.6	12.3	0.029	0.68	2.84	1.5	8.0	0.5	35.4	<0.01	0.13	2.1	<0.005
CC39603		5.2	230	7.5	6.4	0.013	0.37	1.83	1.2	5.4	0.3	23.6	<0.01	0.10	1.2	<0.005
CC39604		11.8	290	10.0	11.4	0.029	0.60	2.99	1.7	8.0	0.5	31.8	<0.01	0.13	2.0	<0.005
CC39606		6.8	880	9.4	9.4	0.028	0.75	8.10	3.6	11.1	0.5	28.4	<0.01	0.16	2.1	<0.005
CC39607		6.8	2680	9.3	9.3	0.024	1.16	12.25	6.2	15.2	0.5	34.4	<0.01	0.19	2.5	<0.005
CC39608		7.9	1280	10.0	10.1	0.032	0.84	10.10	4.0	14.3	0.5	32.9	<0.01	0.18	2.4	<0.005
CC39609		6.8	1110	9.5	10.2	0.031	0.77	9.25	3.7	13.6	0.5	31.7	<0.01	0.19	2.3	<0.005
CC39610		9.1	860	11.5	11.5	0.028	0.58	6.93	3.4	12.5	0.5	32.9	<0.01	0.16	1.9	<0.005
CC39611		12.7	1450	10.8	10.6	0.030	0.74	11.05	5.0	16.1	0.6	54.4	<0.01	0.19	2.7	<0.005
CC39612		8.8	1020	10.3	10.0	0.029	0.64	7.91	3.7	12.5	0.5	32.9	<0.01	0.16	2.2	<0.005
CC39613		22.5	900	12.3	11.9	0.035	0.72	10.40	3.5	17.0	0.6	48.0	<0.01	0.21	2.6	0.005
CC39614		15.6	1550	10.0	9.4	0.027	0.74	10.70	4.7	14.6	0.5	32.9	<0.01	0.19	2.2	<0.005
CC39615		17.5	810	11.6	10.4	0.034	0.62	9.25	3.8	15.1	0.6	39.1	<0.01	0.19	2.5	<0.005
CC39616		29.4	1030	15.1	16.2	0.032	1.08	11.40	4.7	21.6	0.8	71.2	<0.01	0.24	3.1	0.007
CC39617		32.8	860	12.4	12.3	0.034	0.75	10.40	4.4	17.2	0.6	54.3	<0.01	0.22	2.7	0.006
CC39618		16.0	710	10.3	9.5	0.029	0.56	7.82	3.2	12.8	0.5	35.6	<0.01	0.15	2.1	<0.005
CC39619		49.6	760	11.2	9.9	0.030	0.60	11.00	4.1	13.8	0.5	49.3	<0.01	0.17	2.3	0.010
CC39632		116.0	1670	10.3	15.5	0.025	0.12	6.13	5.2	6.2	0.6	382.0	<0.01	0.08	3.9	0.011
CC39633		190.0	1270	10.9	13.0	0.033	0.12	7.71	6.2	8.0	0.7	349.0	0.01	0.09	4.5	0.008

Comments: Interference: Ca>10% on ICP-MS As,ICP-AES results shown. Gold determinations by ME-MS41 are semi-quantitative due to the small sample weight used (0.5g).

ALS Chemex

EXCELLENCE IN ANALYTICAL CHEMISTRY

ALS Canada Ltd.

212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: STRATEGIC METALS LTD.
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO

Finalized Date: 27-JUL-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07077183

Sample Description	Method	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41
	Analyte	Tl	U	V	W	Y	Zn	Zr
	Units	ppm	ppm	ppm	ppm	ppm	ppm	ppm
	LOR	0.02	0.05	1	0.05	0.05	2	0.5
CC39762		0.11	1.18	33	<0.05	11.85	130	3.6
CC39763		0.11	1.20	34	<0.05	12.05	120	3.5
CC39764		0.08	1.14	30	<0.05	10.35	120	5.2
CC39765		0.11	1.26	35	<0.05	12.10	114	3.7
CC39766		0.10	1.18	30	<0.05	11.65	115	4.1
CC39784		0.15	1.90	108	0.09	15.95	285	2.7
CC39785		0.19	1.98	108	0.08	17.70	274	2.5
CC39786		0.17	2.04	112	0.09	17.35	287	2.7
CC39787		0.16	1.96	98	0.06	16.90	261	2.6
CC39788		0.25	2.17	108	0.08	17.80	337	2.7
CC39789		0.46	3.00	111	0.12	18.10	434	3.5
CC39790		0.76	3.40	179	0.14	18.45	431	3.4
CC39791		0.75	3.58	162	0.14	18.15	422	4.3
CC39792		0.88	3.32	151	0.14	17.80	437	3.2
CC39793		0.92	3.20	149	0.13	16.10	358	2.7
CC39794		1.02	3.71	159	0.16	15.55	366	3.7
CC39795		1.07	3.68	155	0.15	14.60	342	4.0
CC39796		0.89	3.26	138	0.13	14.20	336	2.6
CC39797		0.87	3.41	139	0.12	14.80	348	2.9
CC39798		0.78	3.69	132	0.13	13.65	372	4.0
CC39601		1.86	2.64	116	0.19	1.52	13	4.4
CC39602		2.58	3.37	99	0.22	2.67	16	4.6
CC39603		1.73	2.45	68	0.12	2.12	17	1.0
CC39604		2.23	4.25	99	0.22	3.51	22	4.8
CC39606		2.79	13.25	931	0.21	7.56	19	2.4
CC39607		2.68	10.30	1190	0.22	8.44	23	2.1
CC39608		2.47	9.73	521	0.25	6.60	20	3.1
CC39609		2.71	9.93	476	0.23	6.91	21	2.1
CC39610		3.10	9.24	284	0.23	8.95	27	0.7
CC39611		3.02	12.20	389	0.26	7.50	23	3.2
CC39612		2.77	8.91	350	0.22	6.69	23	1.5
CC39613		3.09	10.60	278	0.29	9.19	70	4.3
CC39614		2.85	10.35	503	0.24	8.99	46	1.5
CC39615		2.85	14.80	249	0.28	9.09	63	4.1
CC39616		4.62	19.10	266	0.35	12.20	130	6.9
CC39617		3.27	19.70	267	0.31	11.85	163	5.5
CC39618		2.76	14.40	241	0.22	8.22	70	2.0
CC39619		2.71	18.40	356	0.25	13.40	418	2.8
CC39632		0.65	6.95	312	0.18	24.60	705	3.8
CC39633		0.78	8.99	303	0.23	28.20	1230	4.3

Comments: Interference: Ca>10% on ICP-MS As,ICP-AES results shown. Gold determinations by ME-MS41 are semi-quantitative due to the small sample weight used (0.5g).

ALS Chemex

EXCELLENCE IN ANALYTICAL CHEMISTRY

ALS Canada Ltd.

212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: STRATEGIC METALS LTD.
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO

Finalized Date: 27-JUL-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07077183

Sample Description	Method	WEI-21	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41
	Analyte	Recvd Wt.	Ag	Al	As	Au	B	Ba	Be	Bi	Ca	Cd	Ce	Co	Cr	Cs
	Units	kg	ppm	%	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppm	ppm	ppm
	LOR	0.02	0.01	0.01	0.1	0.2	10	10	0.05	0.01	0.01	0.01	0.02	0.1	1	0.05
CC39634		0.16	0.66	0.85	29.4	<0.2	10	7630	0.84	0.16	5.10	7.90	24.20	10.3	30	1.20
CC39635		0.18	1.14	0.78	28.7	<0.2	<10	4170	0.66	0.27	1.68	17.65	35.40	8.3	32	1.05
CC39636		0.22	0.72	0.64	15.9	<0.2	<10	3940	0.51	0.22	1.28	2.75	28.30	10.6	22	1.24
CC39637		0.18	0.45	0.51	10.4	<0.2	<10	1380	0.46	0.12	8.40	1.23	21.70	5.8	15	0.82
CC39638		0.22	0.48	0.53	10.8	<0.2	<10	1230	0.46	0.14	8.59	1.29	21.10	5.9	14	0.88
CC39639		0.10	0.35	0.81	10	<0.2	<10	270	0.51	0.09	10.85	1.30	25.20	5.0	14	1.03
CC39640		0.14	0.48	0.90	9	<0.2	10	260	0.65	0.10	11.30	1.71	26.40	6.4	15	1.18
CC39641		0.18	0.26	0.72	8	<0.2	<10	210	0.50	0.11	11.65	1.31	28.40	6.0	13	0.89
CC39642		0.16	0.28	0.80	9	<0.2	<10	210	0.41	0.07	11.85	1.00	22.00	4.6	14	0.71
CC39643		0.20	0.29	0.73	8	<0.2	<10	210	0.50	0.09	12.40	1.28	28.60	6.3	13	0.86
CC39644		0.24	0.29	0.77	10	<0.2	<10	300	0.51	0.08	14.15	1.38	27.90	6.3	15	0.80
CC39645		0.14	0.40	0.91	10	<0.2	<10	220	0.59	0.09	11.30	1.37	29.00	6.4	15	0.99
CC39646		0.14	0.42	0.86	14	<0.2	<10	210	0.58	0.09	12.75	1.41	29.30	6.5	15	1.08
CC39647		0.32	0.41	0.90	12	<0.2	<10	490	0.55	0.09	15.10	1.73	26.60	6.6	18	0.83
CC39648		0.18	0.31	0.79	9	<0.2	<10	200	0.51	0.08	13.95	1.33	29.50	6.0	14	0.93
CC39649		0.08	0.32	0.83	8	<0.2	<10	180	0.50	0.08	14.05	1.34	28.60	6.0	15	0.93
CC39650		0.08	0.38	0.84	11	<0.2	<10	190	0.53	0.10	10.50	1.38	26.40	6.1	15	1.12
CC39651		0.22	0.24	0.85	7.5	<0.2	<10	170	0.54	0.10	8.76	0.95	31.20	6.5	14	0.99
CC39652		0.16	0.38	0.88	10.1	<0.2	<10	410	0.59	0.11	8.07	1.38	27.90	6.6	16	0.98
CC39653		0.14	0.31	0.87	12.4	<0.2	<10	500	0.52	0.13	8.57	1.44	26.50	6.6	16	1.01
CC39654		0.08	0.36	0.90	9.9	<0.2	<10	410	0.58	0.11	8.73	1.55	26.90	6.9	16	1.12
CC39655		0.16	0.33	0.86	10.5	<0.2	<10	450	0.54	0.12	8.25	1.46	26.90	7.1	16	1.07
CC39621		0.22	0.47	0.59	12.5	<0.2	<10	1640	0.52	0.20	8.51	1.84	21.40	6.4	18	0.96
CC39622		0.22	0.51	0.56	12.2	<0.2	<10	1490	0.52	0.14	8.08	1.67	21.60	6.7	16	0.94
CC39623		0.22	0.50	0.55	11.6	<0.2	<10	1250	0.48	0.14	8.74	1.28	20.90	6.2	15	0.88
CC39624		Not Recvd														
CC39625		Not Recvd														
CC39626		0.26	0.56	0.82	15.7	<0.2	10	2660	0.65	0.13	9.45	5.11	24.60	7.1	25	1.21
CC39627		0.22	0.71	0.87	17.0	<0.2	10	2480	0.68	0.14	7.84	5.68	25.10	7.3	26	1.39
CC39663		0.30	0.48	0.52	10.9	<0.2	<10	1220	0.46	0.14	8.56	1.27	20.80	6.1	14	0.87
CC27806		0.04	0.99	0.58	14.6	<0.2	<10	2360	0.43	0.21	0.70	5.19	17.95	4.5	14	0.81
CC29665		0.08	0.61	0.77	24.9	<0.2	<10	500	0.56	0.15	1.12	4.88	12.45	5.5	20	0.72
CC20213		0.20	0.20	1.21	21.5	<0.2	<10	560	0.69	0.24	5.40	1.63	21.70	12.1	24	1.32

Comments: Interference: Ca>10% on ICP-MS As,ICP-AES results shown. Gold determinations by ME-MS41 are semi-quantitative due to the small sample weight used (0.5g).

ALS Chemex

EXCELLENCE IN ANALYTICAL CHEMISTRY

ALS Canada Ltd.

212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: STRATEGIC METALS LTD.
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO

Finalized Date: 27-JUL-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07077183

Sample Description	Method	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41
	Analyte	Cu	Fe	Ga	Ge	Hf	Hg	In	K	La	Li	Mg	Mn	Mo	Na	Nb
	Units	ppm	%	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	%	ppm	ppm	%	ppm
	LOR	0.2	0.01	0.05	0.05	0.02	0.01	0.005	0.01	0.2	0.1	0.01	5	0.05	0.01	0.05
CC39634		60.4	2.01	3.10	0.09	0.28	0.23	0.029	0.20	14.1	5.9	2.24	220	61.30	0.13	0.18
CC39635		81.6	2.55	3.06	0.13	0.08	0.25	0.033	0.12	20.4	7.9	0.59	187	46.20	<0.01	0.34
CC39636		60.5	2.72	2.47	0.11	0.09	0.24	0.046	0.15	14.5	6.6	0.51	222	9.21	<0.01	0.12
CC39637		57.6	1.42	1.89	0.07	0.09	0.18	0.024	0.13	11.9	10.1	2.51	230	4.73	0.01	0.07
CC39638		57.1	1.46	1.97	0.07	0.07	0.19	0.025	0.12	11.7	11.0	2.42	228	4.68	0.01	0.08
CC39639		27.0	1.46	2.72	0.09	0.08	0.06	0.017	0.10	13.2	20.8	1.48	108	2.91	0.01	0.14
CC39640		36.3	1.47	3.10	0.10	0.09	0.08	0.020	0.11	13.8	23.9	1.69	222	3.70	0.02	0.17
CC39641		25.4	1.36	2.48	0.09	0.08	0.04	0.021	0.09	14.6	19.3	1.25	222	3.59	0.01	0.12
CC39642		23.7	1.46	2.01	0.08	0.06	0.04	0.014	0.10	10.9	15.7	1.39	244	2.65	0.02	0.10
CC39643		27.9	1.40	2.49	0.10	0.09	0.05	0.019	0.09	14.6	20.0	1.30	229	3.86	0.01	0.13
CC39644		30.5	1.45	2.54	0.10	0.10	0.04	0.018	0.11	14.4	18.6	1.34	277	4.84	0.02	0.12
CC39645		31.1	1.50	2.97	0.09	0.09	0.05	0.020	0.11	14.6	22.3	1.57	241	3.57	0.02	0.16
CC39646		34.3	1.51	2.91	0.10	0.09	0.06	0.020	0.11	14.9	21.8	1.58	252	3.90	0.02	0.15
CC39647		39.6	1.49	3.07	0.10	0.16	0.05	0.020	0.15	13.8	20.8	1.57	292	7.01	0.02	0.12
CC39648		28.5	1.38	2.67	0.10	0.09	0.04	0.018	0.11	14.7	19.6	1.44	234	4.07	0.02	0.13
CC39649		28.5	1.41	2.74	0.09	0.09	0.04	0.018	0.11	14.3	20.0	1.47	231	3.94	0.02	0.13
CC39650		33.6	1.50	2.85	0.10	0.09	0.06	0.020	0.11	13.6	21.5	1.52	207	3.25	0.02	0.14
CC39651		27.0	1.52	2.76	0.10	0.09	0.05	0.019	0.10	15.3	22.2	1.44	108	2.85	0.01	0.14
CC39652		31.8	1.54	2.88	0.09	0.09	0.06	0.022	0.10	14.0	21.3	1.34	170	4.69	0.01	0.14
CC39653		29.3	1.72	2.84	0.09	0.08	0.05	0.023	0.11	14.2	18.9	1.20	201	6.84	0.01	0.13
CC39654		29.8	1.59	3.01	0.09	0.08	0.06	0.022	0.11	14.2	21.4	1.40	215	4.85	0.01	0.15
CC39655		29.3	1.65	2.90	0.09	0.09	0.05	0.022	0.10	14.1	20.1	1.23	197	5.57	0.01	0.14
CC39621		53.1	1.56	2.21	0.08	0.07	0.17	0.025	0.14	11.9	10.8	2.49	232	6.55	0.01	0.11
CC39622		60.6	1.50	2.13	0.08	0.08	0.17	0.027	0.13	12.3	10.9	2.29	222	6.27	0.01	0.11
CC39623		60.8	1.55	1.98	0.07	0.08	0.18	0.024	0.12	11.9	10.9	2.41	229	4.97	0.01	0.10
CC39624																
CC39625																
CC39626		48.4	1.71	2.97	0.11	0.08	0.12	0.025	0.16	14.1	12.4	1.93	198	18.50	0.01	0.21
CC39627		54.1	1.91	3.30	0.12	0.09	0.16	0.029	0.19	14.2	14.8	1.86	181	20.30	0.01	0.23
CC39663		58.8	1.45	1.98	0.07	0.08	0.17	0.025	0.12	11.8	10.8	2.49	225	4.76	0.01	0.10
CC27806		40.5	1.43	2.15	0.08	0.05	0.25	0.026	0.08	9.6	4.8	0.14	148	12.30	<0.01	0.15
CC29665		51.3	3.11	2.37	0.13	0.07	0.23	0.023	0.06	6.2	5.0	0.11	77	21.60	0.01	0.29
CC20213		40.8	2.80	3.86	0.10	0.11	0.06	0.036	0.11	10.7	19.0	0.86	265	7.84	0.01	0.09

Comments: Interference: Ca>10% on ICP-MS As,ICP-AES results shown. Gold determinations by ME-MS41 are semi-quantitative due to the small sample weight used (0.5g).

ALS Chemex
EXCELLENCE IN ANALYTICAL CHEMISTRY
ALS Canada Ltd.
212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: STRATEGIC METALS LTD.
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO

Finalized Date: 27-JUL-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07077183

Sample Description	Method	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41
	Analyte	Ni	P	Pb	Rb	Re	S	Sb	Sc	Se	Sn	Sr	Ta	Te	Th	Ti
	Units	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%
	LOR	0.2	10	0.2	0.1	0.001	0.01	0.05	0.1	0.2	0.2	0.2	0.01	0.01	0.2	0.005
CC39634		183.0	920	10.3	12.7	0.036	0.12	9.02	6.1	6.4	0.7	407.0	0.01	0.10	5.0	0.008
CC39635		180.5	1140	14.8	10.6	0.017	0.10	12.95	5.1	10.4	0.6	197.5	0.01	0.13	3.7	0.010
CC39636		87.3	1150	11.9	10.9	0.028	0.08	5.26	5.9	5.4	0.9	176.0	<0.01	0.07	5.8	0.005
CC39637		27.4	1400	19.5	7.0	0.010	0.22	2.58	3.6	1.9	0.3	205.0	<0.01	0.06	2.9	<0.005
CC39638		29.0	1340	19.4	7.4	0.009	0.22	2.48	3.5	2.1	0.2	216.0	<0.01	0.06	2.7	<0.005
CC39639		19.2	1630	10.1	10.8	0.001	0.07	1.50	2.7	1.6	0.2	610.0	<0.01	0.05	2.5	0.005
CC39640		26.3	1440	11.6	12.6	0.001	0.07	1.70	3.3	1.9	0.3	630.0	<0.01	0.05	2.2	0.006
CC39641		19.4	1980	10.6	9.3	0.001	0.04	1.81	2.4	1.3	0.2	679.0	<0.01	0.05	3.0	<0.005
CC39642		15.4	1900	8.6	7.6	0.001	0.05	1.42	2.0	1.1	0.2	676.0	<0.01	0.04	2.1	0.005
CC39643		19.7	1960	11.4	9.3	0.001	0.04	2.11	2.5	1.5	0.2	730.0	<0.01	0.05	2.9	<0.005
CC39644		21.5	2010	11.2	9.5	0.001	0.04	2.24	2.5	1.5	0.2	845.0	<0.01	0.06	3.1	<0.005
CC39645		21.2	1810	11.6	11.0	0.001	0.05	1.77	2.8	1.4	0.3	639.0	<0.01	0.05	2.7	0.006
CC39646		21.0	1890	11.7	11.2	0.001	0.05	1.98	2.9	1.7	0.2	718.0	<0.01	0.05	2.7	0.005
CC39647		24.5	1740	11.7	11.3	0.003	0.05	3.56	2.8	1.8	0.2	875.0	<0.01	0.07	3.4	0.005
CC39648		18.9	2050	10.6	9.9	0.001	0.06	2.08	2.6	1.5	0.2	810.0	<0.01	0.05	2.9	<0.005
CC39649		19.0	2040	10.9	10.2	0.001	0.06	2.10	2.5	1.5	0.2	824.0	<0.01	0.06	2.9	<0.005
CC39650		20.4	1650	11.7	11.5	0.001	0.07	1.70	2.9	2.1	0.2	580.0	<0.01	0.05	2.3	0.005
CC39651		20.2	1810	11.9	10.6	0.001	0.05	1.32	2.7	1.5	0.2	503.0	<0.01	0.04	3.0	0.005
CC39652		26.1	1580	11.8	10.8	0.002	0.06	3.55	2.9	2.0	0.3	451.0	<0.01	0.05	2.5	0.005
CC39653		28.0	1860	11.9	9.9	0.004	0.06	2.02	2.7	1.9	0.3	503.0	<0.01	0.05	3.0	<0.005
CC39654		27.6	1800	11.5	11.4	0.002	0.06	1.74	2.9	1.8	0.3	491.0	<0.01	0.05	2.8	0.005
CC39655		27.9	1900	11.2	10.0	0.003	0.05	1.82	2.8	1.8	0.3	473.0	<0.01	0.05	3.0	<0.005
CC39621		36.1	1550	18.2	8.5	0.010	0.21	2.79	3.6	2.2	0.3	257.0	<0.01	0.05	3.2	<0.005
CC39622		36.1	1410	18.5	7.8	0.010	0.20	2.84	3.6	2.2	0.3	227.0	<0.01	0.06	3.1	<0.005
CC39623		30.5	1390	20.5	6.9	0.010	0.21	2.60	3.5	1.9	0.3	222.0	<0.01	0.06	2.9	<0.005
CC39624																
CC39625																
CC39626		70.1	1980	9.5	11.5	0.019	0.13	4.54	3.6	3.8	0.4	409.0	<0.01	0.07	3.4	0.007
CC39627		81.9	1720	10.8	14.2	0.019	0.22	5.15	4.0	4.6	0.5	343.0	<0.01	0.08	3.1	0.008
CC39663		29.1	1460	20.2	6.9	0.010	0.20	2.57	3.4	2.0	0.2	214.0	<0.01	0.06	2.9	<0.005
CC27806		35.9	510	11.7	7.8	0.020	0.15	3.71	2.9	8.3	0.5	96.5	<0.01	0.11	2.0	<0.005
CC29665		110.5	560	9.0	7.6	0.047	0.22	6.98	3.1	15.1	0.4	53.5	<0.01	0.10	1.6	0.006
CC20213		52.9	1270	16.3	10.6	0.008	0.12	2.27	4.4	1.8	0.4	306.0	<0.01	0.07	4.0	<0.005

Comments: Interference: Ca>10% on ICP-MS As,ICP-AES results shown. Gold determinations by ME-MS41 are semi-quantitative due to the small sample weight used (0.5g).

ALS Chemex

EXCELLENCE IN ANALYTICAL CHEMISTRY

ALS Canada Ltd.

212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: STRATEGIC METALS LTD.
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO

Finalized Date: 27-JUL-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07077183

Sample Description	Method / Analyte / Units / LOR	ME-MS41 Tl ppm 0.02	ME-MS41 U ppm 0.05	ME-MS41 V ppm 1	ME-MS41 W ppm 0.05	ME-MS41 Y ppm 0.05	ME-MS41 Zn ppm 2	ME-MS41 Zr ppm 0.5
CC39634		0.42	12.95	359	0.26	29.90	797	12.1
CC39635		1.17	6.37	323	0.25	26.60	698	2.6
CC39636		0.44	3.08	90	0.10	18.05	406	3.2
CC39637		0.28	1.26	43	0.09	11.65	175	3.9
CC39638		0.29	1.34	45	0.09	11.65	184	3.0
CC39639		0.19	1.30	58	<0.05	11.75	144	2.8
CC39640		0.24	1.37	63	0.05	13.80	167	3.1
CC39641		0.12	1.38	53	<0.05	12.40	128	3.4
CC39642		0.09	1.08	57	<0.05	9.56	136	2.3
CC39643		0.10	1.44	53	<0.05	12.90	132	3.7
CC39644		0.11	1.56	68	0.05	12.60	149	4.8
CC39645		0.12	1.33	65	<0.05	13.05	145	3.1
CC39646		0.13	1.44	64	<0.05	13.55	145	3.4
CC39647		0.13	1.84	101	0.05	12.60	205	7.7
CC39648		0.11	1.52	64	<0.05	12.95	138	4.1
CC39649		0.11	1.51	66	<0.05	12.75	141	4.0
CC39650		0.11	1.31	57	<0.05	13.20	142	3.0
CC39651		0.10	1.22	48	<0.05	12.40	121	3.2
CC39652		0.27	1.43	74	0.05	13.05	174	2.8
CC39653		0.37	1.89	81	0.06	12.90	183	2.9
CC39654		0.31	1.61	77	0.06	13.30	199	2.8
CC39655		0.30	1.79	82	0.06	13.00	190	2.9
CC39621		0.33	2.03	72	0.09	13.40	225	3.3
CC39622		0.33	1.79	58	0.09	13.20	205	3.5
CC39623		0.30	1.48	47	0.09	12.15	187	3.3
CC39624								
CC39625								
CC39626		0.63	4.47	208	0.12	18.05	514	3.4
CC39627		0.85	4.49	202	0.13	18.50	531	2.9
CC39663		0.29	1.43	45	0.09	12.35	184	3.4
CC27806		1.41	5.24	94	0.14	10.45	235	1.2
CC29665		1.19	8.13	318	0.15	15.85	298	2.2
CC20213		0.37	2.16	104	0.08	11.85	228	4.2

Comments: Interference: Ca>10% on ICP-MS As,ICP-AES results shown. Gold determinations by ME-MS41 are semi-quantitative due to the small sample weight used (0.5g).

ALS Chemex
EXCELLENCE IN ANALYTICAL CHEMISTRY
ALS Canada Ltd.
212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Finalized Date: 12-OCT-2007
Account: MTT

CERTIFICATE VA07069849

Project: NIMO

P.O. No.:

This report is for 14 Rock samples submitted to our lab in Vancouver, BC, Canada on 5-JUL-2007.

The following have access to data associated with this certificate:

AL ARCHER VANCOUVER OFFICE	DOUG EATON BILL WENGZYNOWSKI	JOAN MARIACHER

SAMPLE PREPARATION

ALS CODE	DESCRIPTION
FND-02	Find Sample for Addn Analysis

ANALYTICAL PROCEDURES

ALS CODE	DESCRIPTION
PGM-MS26	PGE Nickel Sulfide Collection

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

This is the Final Report and supersedes any preliminary report with this certificate number. Results apply to samples as submitted. All pages of this report have been checked and approved for release.

Signature:

Lawrence Ng, Laboratory Manager - Vancouver

ALS Chemex
EXCELLENCE IN ANALYTICAL CHEMISTRY
ALS Canada Ltd.
212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: STRATEGIC METALS LTD.
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO

Finalized Date: 12-OCT-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07069849

Sample Description	Method	PGM-MS26	PGM-MS26	PGM-MS26	PGM-MS26	PGM-MS26	PGM-MS26	PGM-MS26
	Analyte	Pt	Pd	Ir	Os	Rh	Ru	Au
	Units	ppb	ppb	ppb	ppb	ppb	ppb	ppb
	LOR	2	2	2	2	2	2	5
C385601		283	158	<2	64	3	6	87
C385603		308	180	<2	31	3	5	119
C385605		224	131	<2	52	3	4	79
C385607		256	143	<2	39	2	4	92
C385609		229	126	<2	23	2	4	75
C385611		228	126	<2	39	2	4	80
C385613		407	258	<2	13	3	5	164
C385615		351	242	<2	11	3	7	120
C385616		322	195	3	74	5	10	96
C385617		491	292	3	36	8	28	337
C385624		466	304	<2	12	2	4	237
C385626		596	372	<2	19	4	7	425
C385632		50	39	<2	2	<2	3	25
C385633		164	106	<2	21	3	6	38

ALS Chemex
EXCELLENCE IN ANALYTICAL CHEMISTRY
ALS Canada Ltd.
212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Finalized Date: 9-JUL-2007
Account: MTT

CERTIFICATE VA07067610

Project: NIMO

P.O. No.:

This report is for 240 Soil samples submitted to our lab in Vancouver, BC, Canada on 28-JUN-2007.

The following have access to data associated with this certificate:

JOAN MARIACHER

SAMPLE PREPARATION

ALS CODE	DESCRIPTION
WEI-21	Received Sample Weight
LOG-22	Sample login - Rcd w/o BarCode
SCR-41	Screen to -180um and save both

ANALYTICAL PROCEDURES

ALS CODE	DESCRIPTION
ME-MS41	51 anal. aqua regia ICPMS

To: **STRATEGIC METALS LTD.**
ATTN: JOAN MARIACHER
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

is is the Final Report and supersedes any preliminary report with this certificate number. Results apply to samples as submitted. All ges of this report have been checked and approved for release.

Signature: Lawrence Ng

Lawrence Ng, Laboratory Manager - Vancouver

ALS Chemex
EXCELLENCE IN ANALYTICAL CHEMISTRY
ALS Canada Ltd.
212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Finalized Date: 9-JUL-2007
Account: MTT

CERTIFICATE VA07067610

Project: NIMO

P.O. No.:

This report is for 240 Soil samples submitted to our lab in Vancouver, BC, Canada on 28-JUN-2007.

The following have access to data associated with this certificate:

JOAN MARIACHER

SAMPLE PREPARATION

ALS CODE	DESCRIPTION
WEI-21	Received Sample Weight
LOG-22	Sample login - Rcd w/o BarCode
SCR-41	Screen to -180um and save both

ANALYTICAL PROCEDURES

ALS CODE	DESCRIPTION
ME-MS41	51 anal. aqua regia ICPMS

To: **STRATEGIC METALS LTD.**
ATTN: JOAN MARIACHER
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

This is the Final Report and supersedes any preliminary report with this certificate number. Results apply to samples as submitted. All pages of this report have been checked and approved for release.

Signature: Lawrence Ng

Lawrence Ng, Laboratory Manager - Vancouver

ALS Chemex

EXCELLENCE IN ANALYTICAL CHEMISTRY

ALS Canada Ltd.

212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: STRATEGIC METALS LTD.
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO

Finalized Date: 9-JUL-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07067610

Sample Description	Method	WEI-21	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41
	Analyte	Recvd Wt.	Ag	Al	As	Au	B	Ba	Be	Bi	Ca	Cd	Ce	Co	Cr	Cs
	Units	kg	ppm	%	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppm	ppm	ppm
	LOR	0.02	0.01	0.01	0.1	0.2	10	10	0.05	0.01	0.01	0.01	0.02	0.1	1	0.05
CC20350		0.10	0.66	0.84	13.6	<0.2	<10	3630	0.61	0.18	1.32	2.19	16.50	11.1	19	0.73
CC20351		Not Recvd														
CC20383		0.16	0.50	0.96	16.1	<0.2	<10	3720	0.61	0.19	1.07	1.76	16.90	10.5	22	0.76
CC20384		0.10	0.78	0.72	12.5	<0.2	10	4460	0.53	0.19	1.36	2.10	15.85	12.3	17	0.88
CC20385		0.14	0.92	0.70	11.0	<0.2	<10	4200	0.45	0.18	1.38	1.89	14.80	11.4	16	0.89
CC20386		0.14	1.03	0.68	8.3	<0.2	10	2090	0.43	0.16	3.06	2.23	18.95	9.9	12	1.11
CC20387		0.14	0.93	0.85	9.5	<0.2	10	1760	0.56	0.14	3.95	3.49	21.70	8.7	16	1.11
CC20388		0.26	0.83	0.65	8.3	<0.2	10	2170	0.45	0.17	2.76	1.87	19.40	9.1	12	1.10
CC20389		0.12	1.12	0.84	9.2	<0.2	<10	1740	0.51	0.14	3.34	4.13	22.00	8.3	16	1.08
CC20390		0.24	0.97	0.67	7.7	<0.2	10	1770	0.44	0.16	2.61	1.64	18.65	10.7	11	1.20
CC20391		0.12	0.99	0.88	8.5	<0.2	10	660	0.57	0.14	3.58	4.81	23.50	7.5	17	0.99
CC20392		0.18	1.06	0.81	9.8	<0.2	10	700	0.53	0.13	7.41	5.82	24.90	7.0	15	0.95
CC20393		0.14	0.86	0.95	11.0	<0.2	10	630	0.62	0.15	3.79	5.05	29.10	8.6	18	1.04
CC20394		0.18	1.03	0.88	9.7	<0.2	<10	480	0.55	0.12	3.33	5.55	27.80	6.9	18	0.91
CC29649		0.14	0.86	0.65	35.6	<0.2	10	550	0.67	0.15	3.44	18.00	23.50	15.0	26	0.98
CC29651		0.10	0.52	0.81	11.3	<0.2	<10	1570	0.60	0.21	1.38	2.53	35.10	12.0	17	1.66
CC29652		0.14	0.47	0.71	16.7	<0.2	10	1710	0.66	0.23	2.29	2.80	32.00	14.4	26	2.21
CC29653		0.12	0.39	0.79	16.8	<0.2	10	2530	0.62	0.18	2.22	4.15	28.90	12.9	26	1.92
CC29654		0.14	0.41	0.77	13.9	<0.2	10	1640	0.63	0.21	2.16	2.68	28.10	14.2	25	1.92
CC29655		0.14	0.50	0.81	17.1	<0.2	10	2370	0.69	0.22	1.53	5.33	31.70	12.9	29	1.90
CC29656		0.18	0.51	0.82	20.6	<0.2	10	2860	0.64	0.19	1.92	10.75	28.60	13.4	30	1.92
CC29657		0.20	0.08	0.61	29.9	<0.2	<10	1050	0.52	0.13	0.08	1.23	19.15	7.3	12	0.28
CC29658		0.18	0.17	0.65	15.7	<0.2	<10	190	0.29	0.14	0.06	0.48	14.15	4.6	11	0.38
CC29659		0.14	0.16	1.05	17.9	<0.2	<10	230	0.32	0.20	0.02	0.37	19.35	3.9	17	1.24
CC29660		0.14	0.28	0.70	11.8	<0.2	<10	230	0.19	0.16	0.03	0.64	25.30	2.9	16	0.97
CC29661		0.18	1.15	1.96	146.5	<0.2	<10	1410	1.08	0.30	0.51	11.30	38.00	15.2	47	1.25
CC29662		0.14	1.27	1.29	53.9	<0.2	<10	1860	0.80	0.21	1.84	23.30	28.60	11.5	45	1.01
CC29663		0.12	1.05	0.87	39.0	<0.2	10	2560	0.65	0.14	2.65	15.50	22.60	5.4	38	0.73
CC29664		0.12	1.01	0.80	20.6	<0.2	<10	2560	0.61	0.12	2.79	13.45	24.50	3.9	37	0.72
CC29666		0.12	0.43	0.64	22.2	<0.2	10	280	0.13	0.19	0.09	0.41	8.15	2.5	13	0.64
CC29667		0.14	0.33	1.18	14.6	<0.2	<10	810	0.44	0.20	0.25	1.35	17.35	11.2	20	0.79
CC29668		0.20	0.31	0.95	14.9	<0.2	<10	580	0.30	0.18	0.09	0.59	18.85	4.1	15	0.71
CC29669		0.14	0.39	1.21	9.6	<0.2	<10	1640	0.61	0.18	0.73	4.98	21.10	16.5	19	0.67
CC29670		0.20	0.16	1.49	15.9	<0.2	<10	480	0.49	0.23	0.10	0.31	13.50	10.4	27	0.94
CC29714		0.10	1.12	0.51	8.1	<0.2	10	690	0.22	0.14	0.18	1.70	12.45	2.2	15	0.79
CC29715		0.16	0.31	1.03	15.4	<0.2	<10	150	0.17	0.30	0.04	0.22	28.00	2.8	17	0.78
CC29716		0.12	0.37	0.49	13.3	<0.2	<10	320	0.13	0.20	0.04	0.34	13.35	0.9	13	0.51
CC29717		0.16	2.16	0.43	7.9	<0.2	<10	1320	0.57	0.12	0.06	7.38	7.66	0.5	16	0.28
CC29718		0.08	0.22	0.63	11.1	<0.2	<10	120	0.09	0.19	0.03	0.37	23.80	2.3	15	0.65
CC29719		0.10	0.48	0.87	16.4	<0.2	<10	860	0.62	0.15	1.02	4.91	19.30	4.6	16	0.52

Comments: Interference: Ca>10% on ICP-MS As,ICP-AES results shown. Gold determinations by ME-MS41 are semi-quantitative due to the small sample weight used (0.5g).

ALS Chemex

EXCELLENCE IN ANALYTICAL CHEMISTRY

ALS Canada Ltd.

212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO

Finalized Date: 9-JUL-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07067610

Sample Description	Method	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41
	Analyte	Cu	Fe	Ga	Ge	Hf	Hg	In	K	La	Li	Mg	Mn	Mo	Na	Nb
	Units	ppm	%	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	%	ppm	ppm	%	ppm
	LOR	0.2	0.01	0.05	0.05	0.02	0.01	0.005	0.01	0.2	0.1	0.01	5	0.05	0.01	0.05
CC20350		42.0	2.60	2.61	0.09	0.06	0.19	0.029	0.09	8.5	6.0	0.34	341	10.95	<0.01	0.32
CC20351																
CC20383		39.9	2.82	3.19	0.08	0.05	0.15	0.029	0.10	8.5	8.0	0.38	254	11.95	<0.01	0.33
CC20384		51.3	2.86	2.20	0.09	0.06	0.16	0.028	0.12	8.0	4.1	0.47	333	12.50	<0.01	0.20
CC20385		55.1	2.80	2.03	0.08	0.06	0.17	0.027	0.13	7.6	3.6	0.48	293	10.90	<0.01	0.17
CC20386		71.9	2.40	1.93	0.10	0.08	0.19	0.026	0.17	10.3	5.7	0.93	218	4.62	0.01	0.16
CC20387		65.1	1.96	2.73	0.09	0.08	0.20	0.022	0.15	12.1	10.4	0.82	280	4.70	0.01	0.32
CC20388		57.8	2.18	1.81	0.09	0.10	0.15	0.028	0.19	10.4	4.4	0.99	232	4.55	<0.01	0.09
CC20389		77.4	1.90	2.71	0.10	0.09	0.23	0.023	0.14	12.6	11.0	0.80	240	4.50	0.01	0.33
CC20390		60.4	2.50	1.81	0.09	0.09	0.17	0.026	0.18	10.0	4.7	1.01	218	4.31	<0.01	0.13
CC20391		76.3	1.70	2.94	0.09	0.09	0.21	0.024	0.12	13.1	12.7	0.73	256	3.77	0.01	0.41
CC20392		83.6	1.41	2.60	0.07	0.10	0.23	0.025	0.11	13.2	14.0	0.75	238	3.83	0.05	0.42
CC20393		75.2	1.80	2.95	0.06	0.10	0.23	0.028	0.12	13.9	15.9	0.79	271	3.83	0.03	0.45
CC20394		81.5	1.49	2.83	0.06	0.10	0.26	0.024	0.11	14.4	15.2	0.78	242	3.90	0.03	0.45
CC29649		84.8	2.27	2.43	0.09	0.17	0.28	0.038	0.13	10.5	5.0	1.18	271	37.20	0.02	0.15
CC29651		48.2	2.90	2.36	0.08	0.05	0.17	0.043	0.12	17.8	10.8	0.68	193	4.33	0.02	0.16
CC29652		52.1	3.29	2.88	0.07	0.08	0.20	0.044	0.16	14.2	12.5	1.27	342	5.16	0.02	0.09
CC29653		43.4	2.78	2.93	0.07	0.07	0.17	0.036	0.16	13.2	11.5	1.27	495	14.50	0.03	0.11
CC29654		43.5	3.19	2.80	0.06	0.06	0.17	0.043	0.16	14.4	12.1	1.19	602	4.94	0.02	0.12
CC29655		51.4	3.00	3.20	0.08	0.07	0.21	0.042	0.16	15.9	13.2	0.88	331	8.80	0.02	0.14
CC29656		55.0	2.79	3.06	0.07	0.07	0.17	0.037	0.16	13.5	11.9	1.13	493	16.90	0.03	0.20
CC29657		34.7	1.48	2.07	0.05	0.05	0.08	0.025	0.08	8.8	4.3	0.11	98	28.80	0.01	0.30
CC29658		21.0	1.56	2.48	<0.05	0.03	0.03	0.022	0.07	6.9	2.2	0.07	54	29.20	0.01	0.33
CC29659		23.3	1.92	5.37	<0.05	0.02	0.05	0.021	0.07	9.1	3.3	0.07	50	29.00	0.02	0.54
CC29660		22.7	1.15	5.67	<0.05	<0.02	0.05	0.014	0.05	11.5	1.2	0.03	31	16.00	0.01	0.36
CC29661		86.7	3.43	6.56	0.21	0.09	0.36	0.072	0.09	18.9	13.2	0.15	198	89.00	0.02	0.70
CC29662		76.1	2.27	4.51	0.10	0.10	0.41	0.035	0.08	14.7	9.7	0.30	235	37.40	0.02	0.61
CC29663		56.0	1.41	3.36	0.10	0.13	0.37	0.027	0.06	12.4	5.0	0.22	135	35.10	0.03	0.36
CC29664		53.5	1.18	2.93	0.07	0.12	0.44	0.023	0.05	12.8	5.1	0.25	86	18.75	0.03	0.34
CC29666		21.9	7.28	2.33	0.09	0.03	0.22	0.022	0.08	3.5	4.4	0.09	37	18.85	0.02	0.28
CC29667		32.7	4.33	3.17	0.07	0.07	0.19	0.039	0.08	7.1	10.7	0.26	143	8.14	0.02	0.45
CC29668		29.8	2.63	3.12	0.07	0.04	0.17	0.032	0.07	8.3	9.2	0.16	48	13.45	0.02	0.41
CC29669		36.0	4.11	3.24	0.07	0.10	0.18	0.037	0.09	9.1	11.3	0.31	310	4.90	0.02	0.36
CC29670		37.6	3.32	5.21	0.05	0.06	0.14	0.048	0.09	5.1	22.2	0.37	120	5.41	0.02	0.25
CC29714		23.8	0.87	2.70	<0.05	<0.02	0.15	0.013	0.09	5.8	2.3	0.08	39	13.25	0.02	0.20
CC29715		15.3	1.98	7.56	<0.05	0.02	0.05	0.023	0.04	12.4	2.6	0.07	56	12.55	0.01	1.04
CC29716		10.3	0.87	3.65	0.05	<0.02	0.05	0.016	0.07	5.7	0.9	0.03	16	15.10	0.02	0.32
CC29717		85.3	0.39	1.47	0.07	0.04	0.11	0.024	0.08	3.3	0.6	0.02	6	13.30	0.01	0.06
CC29718		13.1	1.27	5.64	<0.05	<0.02	0.05	0.011	0.03	10.7	1.3	0.04	42	10.60	0.01	0.63
CC29719		44.7	1.27	2.65	0.05	0.09	0.17	0.027	0.06	9.3	4.7	0.14	172	15.30	0.02	0.33

Comments: Interference: Ca>10% on ICP-MS As,ICP-AES results shown. Gold determinations by ME-MS41 are semi-quantitative due to the small sample weight used (0.5g).

ALS Chemex

EXCELLENCE IN ANALYTICAL CHEMISTRY

ALS Canada Ltd.

212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: STRATEGIC METALS LTD.
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO

Finalized Date: 9-JUL-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07067610

Sample Description	Method	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41
	Analyte	Ni	P	Pb	Rb	Re	S	Sb	Sc	Se	Sn	Sr	Ta	Te	Th	Ti
	Units	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%
	LOR	0.2	10	0.2	0.1	0.001	0.01	0.05	0.1	0.2	0.2	0.2	0.01	0.01	0.2	0.005
CC20350		59.3	780	14.1	9.7	0.010	0.11	3.60	4.2	4.1	0.4	93.4	0.01	0.07	2.3	0.007
CC20351																
CC20383		53.8	830	14.4	10.6	0.012	0.09	4.35	4.1	3.8	0.4	90.2	<0.01	0.09	2.6	0.007
CC20384		67.8	800	13.4	10.1	0.009	0.10	3.58	4.2	4.6	0.4	118.0	<0.01	0.08	2.6	0.006
CC20385		65.8	780	13.3	10.0	0.009	0.11	3.11	4.1	4.8	0.3	120.5	<0.01	0.07	2.4	0.006
CC20386		47.8	1160	16.3	9.6	0.008	0.25	2.74	4.3	4.7	0.2	133.5	<0.01	0.07	3.1	0.005
CC20387		42.5	1620	21.7	10.6	0.006	0.19	3.43	3.4	4.3	0.3	114.5	<0.01	0.08	2.3	0.010
CC20388		41.5	1260	16.0	10.2	0.012	0.19	2.15	4.5	4.1	0.6	136.5	<0.01	0.07	4.1	<0.005
CC20389		47.3	1370	22.0	10.0	0.007	0.18	3.83	3.4	4.7	0.3	106.0	<0.01	0.07	1.9	0.010
CC20390		49.3	1040	15.4	9.7	0.008	0.24	2.21	4.7	4.7	0.2	129.0	<0.01	0.07	3.8	0.005
CC20391		45.6	1350	23.7	9.8	0.005	0.13	3.69	3.2	4.2	0.4	86.2	<0.01	0.07	1.8	0.012
CC20392		46.9	1360	24.1	9.7	0.005	0.27	3.91	3.2	4.0	0.3	168.0	0.01	0.06	1.6	0.011
CC20393		49.3	1510	25.1	11.1	0.005	0.16	3.19	3.7	3.4	0.4	89.0	0.01	0.07	2.3	0.012
CC20394		44.3	1520	24.6	9.7	0.005	0.13	3.91	3.1	3.8	0.3	78.7	0.01	0.06	1.7	0.013
CC29649		140.0	1440	12.4	10.6	0.053	0.27	9.34	5.0	9.8	0.5	243.0	0.01	0.12	3.7	<0.005
CC29651		62.1	690	16.1	12.5	0.003	0.09	1.52	5.7	3.4	0.3	101.0	0.01	0.07	4.4	<0.005
CC29652		75.6	570	13.9	17.8	0.005	0.14	3.36	6.3	3.2	0.7	167.0	<0.01	0.05	5.9	<0.005
CC29653		91.7	720	11.9	16.2	0.009	0.13	3.32	5.4	3.7	0.6	193.0	<0.01	0.06	5.0	<0.005
CC29654		70.6	690	12.9	16.5	0.005	0.14	2.32	5.6	2.9	0.6	159.0	<0.01	0.05	5.2	<0.005
CC29655		100.0	770	12.2	17.4	0.007	0.10	3.42	6.2	3.8	0.7	154.0	<0.01	0.05	5.5	<0.005
CC29656		118.0	770	12.0	16.2	0.014	0.12	5.09	5.4	4.6	0.6	177.0	0.01	0.06	4.9	0.007
CC29657		110.0	180	8.1	6.5	0.005	0.06	2.40	3.1	4.7	0.3	27.4	<0.01	0.12	2.8	0.007
CC29658		67.1	170	9.1	8.1	0.001	0.04	1.81	2.1	1.7	0.4	19.2	<0.01	0.05	2.0	0.005
CC29659		71.0	230	11.0	12.1	<0.001	0.03	1.91	2.1	1.9	0.8	9.1	<0.01	0.07	1.8	0.010
CC29660		46.7	180	9.4	6.4	0.001	0.02	1.94	1.7	1.4	0.9	8.4	<0.01	0.06	0.9	0.015
CC29661		829.0	1170	19.8	13.7	0.008	0.10	18.90	5.9	29.6	1.2	51.2	0.01	0.30	2.5	0.009
CC29662		269.0	600	14.9	11.3	0.010	0.08	13.30	4.6	10.3	0.6	86.8	0.01	0.13	1.9	0.012
CC29663		142.5	1080	9.5	8.2	0.011	0.16	15.15	3.2	12.4	0.5	136.0	0.01	0.11	1.2	0.008
CC29664		118.5	990	8.3	7.5	0.007	0.16	9.00	3.1	7.4	0.4	159.5	0.01	0.08	1.0	0.008
CC29666		24.2	590	12.1	9.3	0.025	0.58	3.17	3.1	13.3	0.5	24.1	<0.01	0.06	2.0	<0.005
CC29667		72.2	580	12.8	11.3	0.013	0.21	1.71	5.2	5.5	0.4	30.6	0.01	0.06	3.2	0.005
CC29668		42.2	480	12.7	9.7	0.013	0.10	2.34	4.0	6.2	0.4	23.2	<0.01	0.05	2.8	0.005
CC29669		210.0	570	12.4	10.5	0.009	0.15	1.16	4.8	3.9	0.4	49.6	0.01	0.05	3.3	0.005
CC29670		46.3	440	17.3	12.3	0.016	0.08	1.06	5.2	2.9	0.6	25.3	<0.01	0.06	3.0	<0.005
CC29714		19.6	940	11.1	8.8	0.004	0.09	4.43	0.6	2.6	0.5	44.8	<0.01	0.09	<0.2	<0.005
CC29715		15.2	220	10.7	7.6	<0.001	0.02	1.84	2.0	1.1	1.0	16.5	<0.01	0.09	2.6	0.023
CC29716		6.6	490	13.0	8.1	0.001	0.13	4.83	1.4	6.2	0.6	104.0	<0.01	0.18	1.4	0.010
CC29717		10.7	830	12.3	5.8	0.004	0.12	13.60	3.4	9.1	0.5	314.0	<0.01	0.21	1.2	<0.005
CC29718		16.9	200	8.6	5.3	<0.001	0.02	4.21	1.3	1.4	0.8	19.3	<0.01	0.08	1.2	0.021
CC29719		97.7	600	10.4	8.8	0.018	0.09	2.93	3.5	5.2	0.4	75.6	<0.01	0.07	1.1	0.005

Comments: Interference: Ca>10% on ICP-MS As,ICP-AES results shown. Gold determinations by ME-MS41 are semi-quantitative due to the small sample weight used (0.5g).

ALS Chemex

EXCELLENCE IN ANALYTICAL CHEMISTRY

ALS Canada Ltd.

212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO

Finalized Date: 9-JUL-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07067610

Sample Description	Method	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41
	Analyte	Tl	U	V	W	Y	Zn	Zr
	Units	ppm	ppm	ppm	ppm	ppm	ppm	ppm
	LOR	0.02	0.05	1	0.05	0.05	2	0.5
CC20350		0.35	3.64	101	0.17	15.20	300	1.8
CC20351								
CC20383		0.35	3.52	117	0.11	13.35	349	1.3
CC20384		0.28	3.16	93	0.09	14.65	324	1.7
CC20385		0.27	3.02	86	0.09	14.50	302	1.7
CC20386		0.21	2.64	52	0.06	13.95	304	2.5
CC20387		0.22	2.61	79	0.08	14.05	375	2.3
CC20388		0.14	2.27	51	0.05	14.50	251	4.5
CC20389		0.24	2.77	78	0.10	15.20	397	2.6
CC20390		0.18	2.36	45	0.05	13.85	255	3.5
CC20391		0.24	2.49	77	0.09	14.60	436	2.7
CC20392		0.22	3.86	73	0.11	15.80	442	3.1
CC20393		0.23	2.79	78	0.11	15.00	404	3.1
CC20394		0.22	3.07	87	0.18	14.95	470	3.0
CC29649		0.98	7.65	309	0.17	26.40	1005	8.6
CC29651		0.22	1.31	46	0.06	18.10	292	1.4
CC29652		0.34	1.55	51	0.11	20.20	383	2.9
CC29653		0.53	4.20	95	0.10	19.65	533	2.7
CC29654		0.30	1.66	55	0.08	17.80	364	2.2
CC29655		0.52	3.16	79	0.10	22.10	604	2.5
CC29656		0.75	4.88	162	0.13	21.40	1005	2.7
CC29657		1.40	2.52	104	0.10	12.45	141	2.1
CC29658		0.91	1.17	139	0.20	4.63	152	1.2
CC29659		1.85	0.97	232	0.18	3.75	170	0.8
CC29660		0.52	0.95	202	0.16	2.76	108	<0.5
CC29661		12.30	9.98	550	0.36	50.50	1925	3.0
CC29662		2.22	7.17	684	0.25	27.40	1740	3.8
CC29663		1.60	5.75	516	0.20	24.90	864	4.8
CC29664		1.42	8.25	426	0.18	20.70	626	4.5
CC29666		0.86	1.68	119	0.09	7.08	78	1.3
CC29667		0.58	2.23	79	0.09	19.55	184	2.2
CC29668		0.72	2.66	104	0.18	12.30	108	1.4
CC29669		0.29	2.31	55	0.07	34.30	775	2.8
CC29670		0.36	0.81	57	0.21	7.20	113	2.1
CC29714		0.56	2.35	121	0.12	3.74	78	<0.5
CC29715		0.52	0.88	225	0.19	2.39	56	0.8
CC29716		2.05	2.55	176	0.20	3.62	29	0.6
CC29717		2.36	11.25	192	0.19	14.05	28	1.3
CC29718		0.52	0.73	250	0.19	2.01	60	<0.5
CC29719		1.00	4.67	197	0.15	19.75	207	2.7

Comments: Interference: Ca>10% on ICP-MS As,ICP-AES results shown. Gold determinations by ME-MS41 are semi-quantitative due to the small sample weight used (0.5g).

ALS Chemex

EXCELLENCE IN ANALYTICAL CHEMISTRY

ALS Canada Ltd.

212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO

Finalized Date: 9-JUL-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07067610

Sample Description	Method	WEI-21	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41
	Analyte	Recvd Wt.	Ag	Al	As	Au	B	Ba	Be	Bi	Ca	Cd	Ce	Co	Cr	Cs
	Units	kg	ppm	%	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppm	ppm	ppm
	LOR	0.02	0.01	0.01	0.1	0.2	10	10	0.05	0.01	0.01	0.01	0.02	0.1	1	0.05
CC29720		0.06	0.96	0.42	7.9	<0.2	<10	410	0.37	0.09	2.44	10.95	13.10	2.1	11	0.54
CC29721		0.12	0.58	0.73	18.1	<0.2	<10	350	0.26	0.20	0.21	4.21	24.10	3.3	24	0.76
CC29722		0.12	0.14	0.76	23.8	<0.2	<10	170	0.13	0.20	0.05	0.67	27.50	3.4	19	0.76
CC29723		0.12	2.30	1.44	117.5	<0.2	<10	390	0.99	0.22	0.21	25.70	15.95	6.8	139	1.13
CC29724		0.12	0.37	0.61	37.2	<0.2	<10	220	0.32	0.16	0.10	5.98	17.60	1.7	57	0.99
CC29725		0.12	5.70	1.29	124.0	<0.2	10	670	1.24	0.25	1.97	63.90	33.80	9.3	96	1.41
CC29726		0.08	3.82	0.98	72.8	<0.2	<10	810	0.88	0.17	3.43	53.80	30.60	7.7	54	0.86
CC29727		0.12	3.42	0.64	77.9	<0.2	10	930	0.80	0.18	4.63	47.20	21.40	9.1	38	0.89
CC29728		0.08	0.61	0.58	12.9	<0.2	10	2080	0.57	0.09	2.30	6.34	15.95	5.4	13	0.38
CC29729		0.20	0.49	0.63	17.1	<0.2	<10	1540	0.70	0.13	0.54	4.06	19.50	5.1	16	0.40
CC29730		0.10	0.50	0.74	23.6	<0.2	10	1820	0.60	0.13	0.89	3.53	18.50	8.1	20	0.52
CC29731		0.10	0.46	0.60	21.8	<0.2	10	1280	0.52	0.12	1.12	3.49	16.20	6.3	15	0.47
CC29732		0.32	0.57	0.56	24.4	<0.2	<10	1130	0.67	0.16	0.73	4.78	16.15	5.3	13	0.38
CC29733		0.16	1.58	0.87	34.7	<0.2	<10	1650	1.14	0.19	1.80	12.05	31.10	8.8	30	0.76
CC29734		0.10	1.89	0.94	61.9	<0.2	10	1930	0.89	0.19	1.40	17.10	28.40	9.3	42	0.63
CC29735		0.04	0.98	0.47	13.0	<0.2	<10	1010	0.44	0.06	4.03	40.70	11.70	2.1	14	0.36
CC29736		0.06	1.10	0.80	27.4	<0.2	<10	1570	0.66	0.11	3.64	15.00	20.10	5.1	26	0.60
CC29737		0.04	0.32	0.32	4.3	<0.2	<10	1260	0.35	0.02	5.65	9.15	11.30	1.7	9	0.13
CC29738		0.28	5.27	0.89	61.9	<0.2	<10	1940	1.05	0.21	1.61	51.30	23.30	6.1	51	1.12
CC29739		0.24	1.10	0.75	36.1	<0.2	<10	2700	0.99	0.21	1.09	10.60	27.60	4.4	53	0.36
CC29740		0.24	0.98	0.56	37.7	<0.2	<10	1980	1.01	0.20	1.25	8.14	46.20	6.7	39	0.33
CC29741		0.24	0.52	0.63	28.3	<0.2	<10	2160	0.75	0.18	0.25	3.41	28.20	1.8	25	0.55
CC29742		0.14	0.26	1.32	14.0	<0.2	<10	760	0.50	0.13	0.87	0.99	27.20	5.7	25	0.85
CC29743		0.08	0.73	1.02	13.2	<0.2	<10	1380	0.71	0.15	2.04	3.56	25.70	4.8	22	0.73
CC29744		0.04	3.24	0.28	4.4	<0.2	<10	430	0.16	0.05	0.81	1.10	5.54	0.6	6	0.29
CC29745		0.04	0.96	0.26	3.9	<0.2	<10	590	0.20	0.06	0.59	1.21	6.56	0.9	6	0.54
CC29746		0.06	0.44	0.79	9.9	<0.2	10	1930	0.60	0.06	3.54	4.25	22.80	3.7	18	0.53
CC29747		0.10	0.94	0.58	39.1	<0.2	10	1540	0.75	0.17	4.04	10.45	36.90	7.9	37	0.75
CC29748		0.14	2.36	0.39	82.5	<0.2	10	200	0.78	0.23	8.70	25.70	16.45	14.4	35	1.24
CC29749		0.18	2.10	0.33	66.0	<0.2	10	420	0.72	0.22	6.12	20.70	17.05	11.4	32	1.21
CC29750		0.16	0.37	0.68	17.9	<0.2	<10	1640	0.83	0.15	0.40	2.51	18.55	4.4	14	0.44
CC29751		0.18	1.41	0.36	49.2	<0.2	10	620	0.72	0.17	6.04	17.40	21.20	10.0	28	0.98
CC29752		0.16	1.10	0.36	46.3	<0.2	<10	570	0.83	0.16	5.54	14.70	24.90	13.0	23	0.99
CC29753		0.18	1.16	0.34	48.3	<0.2	10	630	0.84	0.16	5.24	15.55	25.10	13.0	23	0.99
CC29754		0.16	1.04	0.31	43.8	<0.2	<10	550	0.73	0.16	5.04	14.55	21.60	12.2	21	0.82
CC29755		0.16	1.12	0.37	51.6	<0.2	10	530	0.79	0.15	5.29	15.20	24.00	14.2	22	1.00
CC29756		0.12	0.94	0.35	42.6	<0.2	10	600	0.76	0.15	5.04	13.55	23.80	12.9	23	0.84
CC29757		0.14	0.75	0.36	42.1	<0.2	10	580	0.84	0.16	6.20	12.30	24.30	14.2	19	0.92
CC29758		0.14	1.31	0.54	132.5	<0.2	<10	280	0.76	0.20	4.63	11.50	25.70	12.9	29	0.93
CC29759		0.08	0.28	0.67	25.3	<0.2	<10	1170	0.46	0.09	0.11	0.96	10.65	5.9	12	0.96

Comments: Interference: Ca>10% on ICP-MS As,ICP-AES results shown. Gold determinations by ME-MS41 are semi-quantitative due to the small sample weight used (0.5g).

ALS Chemex

EXCELLENCE IN ANALYTICAL CHEMISTRY

ALS Canada Ltd.

212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: STRATEGIC METALS LTD.
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO

Finalized Date: 9-JUL-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07067610

Sample Description	Method	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41
	Analyte	Cu	Fe	Ga	Ge	Hf	Hg	In	K	La	Li	Mg	Mn	Mo	Na	Nb
	Units	ppm	%	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	%	ppm	ppm	%	ppm
	LOR	0.2	0.01	0.05	0.05	0.02	0.01	0.005	0.01	0.2	0.1	0.01	5	0.05	0.01	0.05
CC29720		24.6	0.71	1.64	<0.05	0.06	0.20	0.016	0.04	6.6	1.0	0.06	30	11.15	0.03	0.22
CC29721		26.8	1.37	4.97	0.05	<0.02	0.09	0.021	0.05	11.7	2.0	0.07	105	18.95	0.02	0.40
CC29722		19.1	1.73	6.28	0.05	<0.02	0.05	0.021	0.04	12.6	2.9	0.07	71	24.90	0.02	0.76
CC29723		127.0	1.89	8.68	0.15	0.04	0.34	0.047	0.11	11.6	6.2	0.10	82	95.10	0.01	0.30
CC29724		49.6	1.11	5.39	0.07	<0.02	0.07	0.020	0.05	11.4	1.7	0.04	30	30.30	0.02	0.32
CC29725		169.5	2.05	6.03	0.18	0.10	1.14	0.036	0.16	25.7	8.1	0.30	108	117.00	0.02	0.44
CC29726		112.5	1.58	3.95	0.13	0.10	0.72	0.028	0.08	22.7	5.6	0.22	158	59.70	0.03	0.43
CC29727		111.0	1.51	3.45	0.15	0.13	0.53	0.027	0.08	13.2	3.9	0.68	152	58.80	0.03	0.32
CC29728		38.5	1.06	1.95	0.06	0.10	0.13	0.017	0.04	8.4	3.0	0.12	202	19.00	0.03	0.23
CC29729		45.4	1.39	2.34	0.06	0.08	0.13	0.025	0.06	9.9	4.1	0.12	90	27.20	0.01	0.25
CC29730		40.5	1.64	2.77	0.05	0.10	0.16	0.023	0.06	9.4	5.2	0.13	234	31.10	0.02	0.29
CC29731		39.6	1.62	2.21	0.05	0.11	0.15	0.023	0.05	8.2	3.8	0.11	330	29.50	0.02	0.25
CC29732		51.6	1.76	2.11	0.07	0.12	0.19	0.028	0.07	8.3	2.7	0.07	56	29.30	0.02	0.22
CC29733		98.7	1.78	3.31	0.11	0.14	0.48	0.034	0.07	19.2	5.0	0.11	112	32.10	0.02	0.40
CC29734		76.1	1.97	4.07	0.10	0.14	0.33	0.037	0.08	14.3	7.5	0.19	213	48.60	0.02	0.51
CC29735		45.1	0.56	1.72	0.07	0.09	0.22	0.010	0.02	10.0	1.4	0.06	54	7.63	0.03	0.26
CC29736		42.2	1.13	3.01	0.08	0.09	0.19	0.020	0.04	12.7	4.9	0.11	122	20.50	0.02	0.44
CC29737		12.1	0.29	0.92	0.05	0.06	0.15	0.007	0.01	9.3	0.4	0.07	87	1.43	0.02	0.21
CC29738		125.0	1.81	4.14	0.12	0.08	0.86	0.037	0.09	15.8	5.6	0.39	61	46.30	0.02	0.31
CC29739		97.9	1.65	3.43	0.06	0.08	0.32	0.033	0.06	12.3	4.5	0.15	135	31.50	0.02	0.25
CC29740		80.1	1.73	2.70	0.09	0.13	0.44	0.032	0.06	26.6	3.8	0.14	133	60.10	0.02	0.27
CC29741		64.9	1.40	3.47	0.06	0.04	0.29	0.027	0.05	14.6	3.8	0.06	12	14.10	0.02	0.31
CC29742		16.5	1.66	4.83	0.06	0.08	0.12	0.023	0.07	12.8	18.7	0.68	98	4.64	0.02	0.53
CC29743		41.5	1.52	4.03	0.12	0.09	0.17	0.029	0.04	12.7	9.5	0.33	84	4.68	0.02	0.55
CC29744		17.6	0.41	0.67	0.08	0.05	0.35	0.010	0.02	2.4	0.4	0.03	5	2.86	0.02	0.11
CC29745		24.9	0.44	0.95	0.05	0.04	0.14	0.013	0.03	3.0	0.4	0.03	7	7.07	0.02	0.10
CC29746		31.9	0.97	2.71	0.08	0.13	0.13	0.015	0.06	13.0	14.3	0.93	191	8.80	0.03	0.26
CC29747		80.4	1.69	2.92	0.11	0.22	0.30	0.024	0.09	22.9	5.6	0.99	201	40.00	0.03	0.24
CC29748		121.5	1.95	3.31	0.15	0.48	0.29	0.033	0.12	6.7	2.3	2.43	141	101.00	0.03	0.12
CC29749		101.0	1.84	2.68	0.15	0.50	0.34	0.033	0.11	7.7	2.1	2.42	147	80.40	0.03	0.11
CC29750		41.1	1.80	2.24	0.06	0.11	0.18	0.028	0.07	9.2	3.5	0.09	43	19.55	0.01	0.26
CC29751		84.6	1.66	2.23	0.11	0.29	0.28	0.030	0.10	10.9	2.3	1.46	157	53.80	0.02	0.13
CC29752		88.2	2.04	2.00	0.11	0.27	0.21	0.038	0.10	12.5	2.3	1.26	195	54.90	0.02	0.11
CC29753		91.0	2.00	2.12	0.11	0.27	0.22	0.037	0.09	12.6	2.2	1.22	183	55.20	0.02	0.12
CC29754		83.9	2.04	1.75	0.11	0.27	0.20	0.036	0.09	10.6	1.7	1.14	192	52.30	0.02	0.09
CC29755		90.9	2.34	2.02	0.12	0.23	0.19	0.043	0.11	11.3	2.2	1.15	204	60.00	0.02	0.11
CC29756		81.2	2.16	1.79	0.10	0.24	0.21	0.035	0.09	11.7	2.1	1.18	212	47.80	0.02	0.11
CC29757		81.3	2.60	1.60	0.10	0.24	0.17	0.041	0.10	11.0	1.7	0.99	237	52.00	0.03	0.10
CC29758		99.0	5.12	2.29	0.22	0.13	0.18	0.068	0.17	12.1	3.5	0.80	215	108.00	0.03	0.14
CC29759		25.4	1.67	1.95	<0.05	0.02	0.07	0.018	0.05	4.6	7.8	0.11	159	15.80	0.01	0.28

Comments: Interference: Ca>10% on ICP-MS As,ICP-AES results shown. Gold determinations by ME-MS41 are semi-quantitative due to the small sample weight used (0.5g).

ALS Chemex

EXCELLENCE IN ANALYTICAL CHEMISTRY

ALS Canada Ltd.

212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: STRATEGIC METALS LTD.
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO

Finalized Date: 9-JUL-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07067610

Sample Description	Method	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41
	Analyte	Ni	P	Pb	Rb	Re	S	Sb	Sc	Se	Sn	Sr	Ta	Te	Th	Ti
	Units	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%
	LOR	0.2	10	0.2	0.1	0.001	0.01	0.05	0.1	0.2	0.2	0.2	0.01	0.01	0.2	0.005
CC29720		47.5	720	8.6	3.8	0.003	0.17	3.75	3.1	4.6	0.3	119.0	0.01	0.06	0.8	0.008
CC29721		62.1	390	12.0	6.4	0.001	0.03	5.25	1.2	3.1	0.7	20.0	<0.01	0.07	0.2	0.015
CC29722		79.9	170	10.0	6.1	<0.001	0.02	5.22	1.6	3.3	0.8	8.8	<0.01	0.09	1.3	0.025
CC29723		231.0	730	23.0	15.1	0.003	0.10	43.20	2.7	26.4	0.9	30.7	0.01	0.32	0.4	0.007
CC29724		63.5	370	14.6	7.8	0.002	0.06	27.90	1.5	10.5	0.6	17.6	<0.01	0.18	0.2	0.014
CC29725		537.0	1420	26.3	15.7	0.012	0.09	48.40	7.3	23.7	0.7	116.0	0.01	0.26	2.5	0.014
CC29726		340.0	1230	17.0	9.0	0.011	0.14	31.50	4.4	17.4	0.5	169.5	0.01	0.15	0.8	0.012
CC29727		285.0	1080	14.4	9.6	0.011	0.12	31.40	3.9	22.0	0.6	226.0	0.01	0.15	1.0	0.008
CC29728		91.4	740	6.3	6.2	0.004	0.13	5.88	2.4	4.1	0.4	119.0	0.01	0.05	0.9	0.005
CC29729		62.0	440	7.9	7.9	0.006	0.03	4.20	3.6	2.5	0.4	46.8	<0.01	0.08	2.3	<0.005
CC29730		60.8	550	9.3	9.2	0.006	0.06	5.56	3.3	2.8	0.4	56.7	<0.01	0.07	1.9	0.005
CC29731		72.5	510	8.8	7.6	0.008	0.06	5.43	3.1	3.2	0.4	65.4	<0.01	0.08	1.6	<0.005
CC29732		95.6	270	10.8	7.8	0.007	0.04	4.08	3.6	4.0	0.5	46.4	<0.01	0.08	1.9	<0.005
CC29733		249.0	420	13.2	10.2	0.006	0.07	11.05	6.1	6.8	0.6	83.0	0.01	0.13	1.6	0.006
CC29734		214.0	520	13.7	8.4	0.005	0.10	21.80	4.7	10.7	0.7	81.4	0.01	0.15	2.2	0.009
CC29735		67.4	800	4.8	2.8	0.002	0.19	8.29	1.7	5.8	0.2	159.5	0.01	0.04	0.3	0.008
CC29736		105.0	760	8.2	5.4	0.006	0.15	11.70	2.7	8.0	0.4	115.5	0.01	0.08	0.6	0.008
CC29737		17.7	910	2.7	1.2	0.007	0.20	1.26	0.8	3.7	<0.2	118.0	0.01	0.02	<0.2	0.005
CC29738		257.0	780	13.0	12.0	0.005	0.08	23.00	7.4	13.1	0.8	88.7	0.01	0.14	1.4	0.009
CC29739		183.5	600	11.3	7.0	0.002	0.08	10.30	3.6	3.8	0.7	84.2	0.01	0.13	2.0	0.005
CC29740		292.0	610	12.3	6.0	0.001	0.07	10.15	4.8	4.2	1.0	102.5	0.01	0.12	3.0	0.006
CC29741		70.8	460	12.3	9.1	0.002	0.07	5.76	3.0	3.2	0.8	49.9	<0.01	0.10	1.5	0.006
CC29742		24.6	950	9.9	10.7	0.005	0.04	2.95	2.7	3.2	0.5	47.0	<0.01	0.05	2.5	0.013
CC29743		44.6	930	10.7	8.0	0.010	0.12	8.53	3.3	20.7	0.5	110.0	<0.01	0.08	1.7	0.009
CC29744		19.5	670	3.3	1.1	0.019	0.17	7.16	2.1	15.5	0.2	58.7	0.01	0.04	0.6	0.005
CC29745		23.0	490	4.6	2.6	0.009	0.12	3.74	2.0	6.4	0.3	67.6	<0.01	0.06	0.7	0.005
CC29746		70.2	1040	6.4	6.5	0.017	0.14	3.49	1.9	3.1	0.4	175.0	<0.01	0.03	0.8	0.006
CC29747		151.0	1720	13.6	8.8	0.044	0.20	11.00	3.7	9.6	0.6	285.0	<0.01	0.12	3.1	0.007
CC29748		287.0	1020	16.7	10.6	0.114	1.10	27.80	5.5	25.7	0.9	350.0	0.01	0.21	4.3	0.005
CC29749		246.0	760	15.2	9.1	0.149	0.38	18.75	5.6	25.0	0.9	208.0	<0.01	0.15	4.9	<0.005
CC29750		74.7	290	10.5	8.7	0.017	0.05	2.42	3.9	7.4	0.5	41.3	<0.01	0.06	3.4	<0.005
CC29751		183.5	800	12.4	8.8	0.099	0.32	13.20	4.8	14.2	0.7	260.0	<0.01	0.12	4.0	<0.005
CC29752		190.0	870	11.6	9.2	0.074	0.36	10.80	5.6	14.5	0.6	252.0	<0.01	0.13	4.1	<0.005
CC29753		190.5	830	12.0	8.9	0.079	0.35	11.40	5.7	15.0	0.7	238.0	0.01	0.11	4.2	<0.005
CC29754		195.5	700	11.8	7.5	0.080	0.34	10.05	5.4	13.9	0.6	221.0	0.01	0.12	4.2	<0.005
CC29755		209.0	880	12.1	9.4	0.086	0.37	11.45	6.0	16.9	0.7	237.0	0.01	0.13	4.2	<0.005
CC29756		185.0	820	11.2	7.9	0.083	0.33	9.31	5.3	12.6	0.5	235.0	0.01	0.12	4.1	<0.005
CC29757		211.0	840	12.6	8.9	0.071	0.38	8.40	6.1	13.6	0.5	277.0	0.01	0.12	4.5	<0.005
CC29758		239.0	1870	19.3	11.5	0.100	0.63	16.40	6.5	38.8	0.8	274.0	0.01	0.37	4.8	<0.005
CC29759		40.5	530	7.9	7.6	0.004	0.06	2.44	2.3	3.6	0.3	22.5	<0.01	0.03	1.4	0.005

Comments: Interference: Ca>10% on ICP-MS As,ICP-AES results shown. Gold determinations by ME-MS41 are semi-quantitative due to the small sample weight used (0.5g).

ALS Chemex

EXCELLENCE IN ANALYTICAL CHEMISTRY

ALS Canada Ltd.

212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: STRATEGIC METALS LTD.
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO

Finalized Date: 9-JUL-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07067610

Sample Description	Method	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41
	Analyte	Tl	U	V	W	Y	Zn	Zr
	Units	ppm	ppm	ppm	ppm	ppm	ppm	ppm
	LOR	0.02	0.05	1	0.05	0.05	2	0.5
CC29720		0.56	2.64	108	0.10	11.00	181	2.1
CC29721		1.09	1.61	285	0.19	4.85	287	<0.5
CC29722		1.73	0.90	395	0.22	2.82	199	<0.5
CC29723		7.54	5.92	2260	0.46	24.50	1795	0.8
CC29724		1.44	2.76	945	0.25	8.02	349	<0.5
CC29725		6.63	12.90	2190	0.46	46.80	6590	3.8
CC29726		3.51	14.40	1040	0.30	42.10	4000	3.4
CC29727		2.04	9.85	884	0.29	39.30	3230	5.1
CC29728		0.48	3.07	168	0.13	17.50	446	3.6
CC29729		0.67	3.38	225	0.17	20.10	347	3.0
CC29730		0.85	3.93	320	0.17	15.85	396	3.2
CC29731		0.86	2.96	254	0.18	16.05	424	3.7
CC29732		0.79	3.94	229	0.16	19.05	432	4.4
CC29733		2.75	10.40	457	0.27	52.40	1175	5.3
CC29734		2.84	4.33	676	0.29	24.80	1820	5.3
CC29735		0.46	7.09	206	0.08	21.60	799	3.8
CC29736		0.85	5.31	388	0.15	20.70	648	3.9
CC29737		0.12	5.66	65	<0.05	20.60	89	2.6
CC29738		2.16	4.45	804	0.26	48.90	3930	2.6
CC29739		1.04	6.56	665	0.40	27.90	787	2.6
CC29740		1.59	7.61	496	0.43	37.90	714	4.9
CC29741		1.35	8.01	350	0.26	20.90	166	1.1
CC29742		0.33	2.18	198	0.14	9.05	196	2.1
CC29743		0.65	11.45	221	0.14	14.85	172	3.2
CC29744		0.09	3.94	25	<0.05	4.40	11	1.9
CC29745		0.39	4.04	48	<0.05	3.85	77	1.6
CC29746		0.49	4.15	145	0.10	16.70	379	3.8
CC29747		1.37	11.40	488	0.31	27.60	735	9.1
CC29748		1.48	17.35	785	0.36	26.30	2330	19.8
CC29749		1.21	14.35	576	0.32	24.80	1750	20.2
CC29750		0.59	6.70	204	0.12	15.15	206	4.7
CC29751		1.22	11.90	468	0.25	25.70	1300	13.4
CC29752		1.24	11.05	351	0.23	31.90	1135	13.7
CC29753		1.32	11.60	349	0.24	32.70	1100	13.9
CC29754		1.29	10.95	307	0.24	29.70	1105	12.3
CC29755		1.49	11.00	338	0.23	32.80	1180	12.2
CC29756		1.36	11.20	324	0.22	30.90	1050	11.4
CC29757		1.67	11.25	249	0.24	35.70	946	10.9
CC29758		6.27	12.35	297	0.35	36.60	991	6.3
CC29759		0.52	3.07	112	0.09	7.73	162	0.6

Comments: Interference: Ca>10% on ICP-MS As,ICP-AES results shown. Gold determinations by ME-MS41 are semi-quantitative due to the small sample weight used (0.5g).

ALS Chemex

EXCELLENCE IN ANALYTICAL CHEMISTRY

ALS Canada Ltd.

212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: STRATEGIC METALS LTD.
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO

Finalized Date: 9-JUL-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07067610

Sample Description	Method / Analyte / Units / LOR	WEI-21 Recvd Wt. kg 0.02	ME-MS41 Ag ppm 0.01	ME-MS41 Al % 0.01	ME-MS41 As ppm 0.1	ME-MS41 Au ppm 0.2	ME-MS41 B ppm 10	ME-MS41 Ba ppm 10	ME-MS41 Be ppm 0.05	ME-MS41 Bi ppm 0.01	ME-MS41 Ca % 0.01	ME-MS41 Cd ppm 0.01	ME-MS41 Ce ppm 0.02	ME-MS41 Co ppm 0.1	ME-MS41 Cr ppm 1	ME-MS41 Cs ppm 0.05
CC29760		0.12	0.82	1.32	60.7	<0.2	10	3680	1.60	0.18	0.36	12.05	34.40	23.7	46	2.18
CC29761		0.14	0.46	0.50	8.9	<0.2	<10	2060	0.51	0.18	6.22	2.84	31.90	13.9	13	1.60
CC29762		0.16	0.83	0.52	12.8	<0.2	<10	1240	0.63	0.29	1.69	4.11	31.90	18.5	13	1.71
CC29765		0.16	0.98	0.84	9.8	<0.2	<10	460	0.56	0.13	2.99	4.59	23.20	6.6	17	0.97
CC29766		0.14	0.94	0.85	9.4	<0.2	<10	440	0.54	0.13	2.98	4.53	24.00	6.6	17	0.97
CC29767		0.22	0.71	0.98	14.5	<0.2	<10	550	0.77	0.19	2.59	4.25	27.80	9.8	20	0.99
CC29771		0.10	0.24	1.59	8.7	<0.2	<10	1000	0.55	0.21	0.55	0.34	30.40	8.4	25	0.95
CC29772		0.10	0.26	1.53	5.7	<0.2	<10	1410	0.73	0.23	0.26	0.72	35.50	6.8	24	0.83
CC29773		0.10	0.32	1.64	10.1	<0.2	<10	1400	0.66	0.24	0.27	0.55	38.90	7.7	27	0.92
CC29774		0.12	0.24	1.62	6.2	<0.2	<10	1410	0.62	0.22	0.24	0.35	35.60	8.1	26	0.94
CC29775		0.10	0.23	1.58	8.7	<0.2	<10	1630	0.60	0.22	0.32	0.26	30.80	8.2	24	0.85
CC29776		0.12	0.22	1.57	10.2	<0.2	<10	1680	0.63	0.22	0.19	0.26	32.80	8.0	26	0.84
CC29777		0.10	0.27	1.53	8.7	<0.2	<10	1840	0.68	0.23	0.23	0.36	34.80	8.6	24	0.82
CC29778		0.12	0.27	1.57	6.6	<0.2	<10	1860	0.53	0.22	0.23	0.23	29.60	7.3	24	0.83
CC29779		0.14	0.24	1.53	7.4	<0.2	<10	1610	0.52	0.22	0.14	0.22	32.40	6.4	24	0.88
CC29780		0.10	0.24	1.60	9.1	<0.2	<10	1610	0.53	0.23	0.20	0.20	32.00	8.5	25	0.95
CC29781		0.08	0.28	1.60	9.6	<0.2	<10	1930	0.55	0.23	0.17	0.26	35.00	7.1	24	0.95
CC29782		0.10	0.31	1.34	4.2	<0.2	<10	1910	0.34	0.17	0.20	0.12	22.70	3.9	21	0.58
CC29783		0.10	0.41	1.60	7.1	<0.2	<10	2390	0.58	0.23	0.14	0.20	34.20	7.9	24	0.92
CC29784		0.10	0.39	1.32	5.1	<0.2	<10	2760	0.44	0.21	0.16	0.15	28.30	4.5	20	0.73
CC29785		0.08	0.45	1.42	4.2	<0.2	<10	2360	0.46	0.23	0.13	0.21	29.90	4.2	21	0.76
CC29786		0.14	0.52	1.48	4.1	<0.2	<10	2480	0.44	0.22	0.15	0.17	30.60	5.3	21	0.74
CC29787		0.14	0.71	1.19	6.4	<0.2	<10	4080	0.56	0.22	0.18	0.42	25.30	6.3	18	0.70
CC29788		0.12	0.48	1.45	4.2	<0.2	<10	3320	0.63	0.22	0.21	0.46	30.00	6.5	22	0.77
CC29789		0.12	0.47	1.41	8.4	<0.2	<10	3980	0.67	0.21	0.16	0.68	29.10	6.0	26	0.75
CC29790		0.10	0.41	1.42	7.5	<0.2	<10	3650	0.62	0.23	0.17	0.55	29.80	6.2	24	0.74
CC29791		0.10	0.83	0.97	25.2	<0.2	<10	3680	1.14	0.20	0.94	9.38	35.80	9.3	48	0.61
CC29792		0.14	2.29	0.70	87.6	<0.2	10	770	0.90	0.27	5.97	32.80	23.90	8.9	50	1.21
CC29793		0.14	0.36	0.55	26.9	<0.2	<10	480	0.76	0.15	0.76	3.99	12.80	7.9	17	0.42
CC29794		0.12	0.31	0.48	20.6	<0.2	<10	630	0.97	0.15	0.27	19.00	14.70	11.1	13	0.44
CC29795		0.16	0.22	0.64	23.6	<0.2	<10	380	0.85	0.14	0.37	4.84	13.55	4.5	15	0.60
CC29796		0.08	0.76	1.20	25.9	<0.2	<10	810	0.65	0.24	0.24	2.05	20.40	6.9	27	0.80
CC29797		0.08	0.35	1.26	12.9	<0.2	<10	510	0.51	0.20	0.22	0.63	19.85	3.5	22	0.75
CC29798		0.08	0.26	1.54	12.2	<0.2	<10	300	0.42	0.21	0.11	0.28	21.30	3.7	25	0.99
CC29799		0.06	0.73	0.41	10.2	<0.2	<10	430	0.18	0.09	0.44	0.43	4.62	1.4	8	0.63
CC29800		0.08	0.60	1.09	26.5	<0.2	10	690	0.72	0.18	2.25	8.43	15.50	7.8	28	0.65
CC29801		0.08	1.04	0.94	41.5	<0.2	10	810	0.95	0.20	2.77	10.55	23.00	8.5	46	0.56
CC29802		0.08	0.29	0.67	15.4	<0.2	10	770	0.68	0.11	3.48	3.46	24.20	4.6	26	0.46
CC29803		0.06	0.29	0.83	18.5	<0.2	<10	900	0.67	0.16	1.96	3.76	23.20	9.5	22	0.57
CC29804		0.10	0.36	1.00	22.5	<0.2	<10	1920	0.36	0.15	0.17	2.87	13.10	4.2	22	0.97

Comments: Interference: Ca>10% on ICP-MS As,ICP-AES results shown. Gold determinations by ME-MS41 are semi-quantitative due to the small sample weight used (0.5g).

ALS Chemex

EXCELLENCE IN ANALYTICAL CHEMISTRY

ALS Canada Ltd.

212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: STRATEGIC METALS LTD.
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO

Finalized Date: 9-JUL-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07067610

Sample Description	Method	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41
	Analyte	Cu	Fe	Ga	Ge	Hf	Hg	In	K	La	Li	Mg	Mn	Mo	Na	Nb
	Units	ppm	%	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	%	ppm	ppm	%	ppm
	LOR	0.2	0.01	0.05	0.05	0.02	0.01	0.005	0.01	0.2	0.1	0.01	5	0.05	0.01	0.05
CC29760		101.0	2.67	5.15	0.13	0.11	0.19	0.037	0.16	16.5	19.5	0.48	643	64.20	0.02	1.19
CC29761		50.9	2.42	1.58	0.07	0.05	0.08	0.033	0.11	14.1	7.2	2.51	389	4.47	0.03	0.08
CC29762		78.0	3.37	1.60	0.08	0.08	0.10	0.039	0.11	15.2	6.1	0.80	460	6.29	0.02	0.09
CC29765		71.9	1.51	2.75	0.09	0.11	0.17	0.021	0.10	13.6	14.5	0.83	229	4.07	0.02	0.42
CC29766		69.6	1.46	2.80	0.09	0.11	0.17	0.021	0.11	14.0	14.4	0.82	245	4.00	0.01	0.43
CC29767		65.5	2.17	3.30	0.10	0.10	0.19	0.032	0.14	15.6	16.0	0.78	321	6.03	0.01	0.35
CC29771		20.4	2.35	4.94	0.08	0.04	0.06	0.031	0.09	15.2	15.4	0.38	177	1.20	0.01	0.55
CC29772		27.3	1.77	5.09	0.07	0.07	0.06	0.031	0.08	17.1	15.8	0.35	87	0.34	<0.01	0.62
CC29773		31.0	2.58	5.41	0.09	0.08	0.07	0.036	0.10	18.9	16.3	0.38	92	0.47	0.01	0.69
CC29774		24.6	2.19	5.03	0.08	0.08	0.06	0.030	0.09	17.6	16.1	0.38	101	0.44	0.01	0.66
CC29775		22.0	2.86	4.96	0.07	0.04	0.06	0.030	0.09	15.7	14.5	0.35	164	0.85	<0.01	0.55
CC29776		25.2	2.69	4.81	0.08	0.07	0.06	0.031	0.09	16.0	14.6	0.35	111	1.34	<0.01	0.54
CC29777		28.7	2.46	4.89	0.08	0.06	0.05	0.033	0.09	16.9	14.5	0.33	101	0.86	<0.01	0.53
CC29778		24.6	2.64	4.45	0.08	0.05	0.06	0.030	0.09	14.9	13.1	0.34	104	0.50	<0.01	0.48
CC29779		23.1	2.31	4.55	0.07	0.06	0.23	0.028	0.08	16.2	14.0	0.35	92	0.45	<0.01	0.49
CC29780		22.1	2.67	5.06	0.07	0.04	0.11	0.030	0.09	16.1	14.9	0.35	141	0.88	<0.01	0.56
CC29781		27.3	2.73	5.00	0.08	0.06	0.10	0.031	0.09	17.2	14.0	0.36	84	0.68	<0.01	0.53
CC29782		16.8	2.16	3.71	0.05	0.03	0.08	0.021	0.09	11.5	9.7	0.30	80	0.78	<0.01	0.34
CC29783		27.4	2.52	4.94	0.07	0.06	0.11	0.033	0.10	17.4	15.1	0.38	99	0.67	<0.01	0.46
CC29784		26.0	2.08	3.85	0.06	0.05	0.12	0.028	0.08	14.4	11.7	0.30	62	0.38	<0.01	0.39
CC29785		24.7	2.14	4.32	0.07	0.05	0.15	0.029	0.09	15.4	13.4	0.31	66	0.45	<0.01	0.41
CC29786		24.1	2.16	4.48	0.07	0.05	0.13	0.028	0.10	15.4	14.4	0.33	94	0.96	<0.01	0.42
CC29787		33.3	2.58	3.33	0.07	0.04	0.16	0.029	0.11	13.2	10.1	0.26	121	3.80	<0.01	0.25
CC29788		30.6	1.76	4.32	0.07	0.05	0.11	0.030	0.09	15.0	12.9	0.31	80	0.66	<0.01	0.38
CC29789		36.0	3.97	4.08	0.08	0.05	0.12	0.031	0.10	14.9	11.0	0.28	129	4.73	<0.01	0.46
CC29790		36.1	2.13	4.46	0.07	0.04	0.11	0.031	0.10	15.0	12.2	0.28	76	3.46	<0.01	0.42
CC29791		85.5	1.83	3.93	0.10	0.15	0.39	0.034	0.08	19.2	8.1	0.23	402	28.00	<0.01	0.35
CC29792		129.5	2.18	3.74	0.14	0.15	1.03	0.036	0.17	13.7	3.9	1.64	107	86.30	0.02	0.21
CC29793		48.8	1.56	1.68	0.07	0.08	0.17	0.025	0.07	9.2	2.1	0.08	113	32.50	0.01	0.13
CC29794		69.0	1.91	1.47	0.08	0.11	0.13	0.028	0.08	9.5	1.3	0.04	324	37.00	<0.01	0.12
CC29795		60.7	2.07	2.13	0.07	0.04	0.12	0.032	0.06	7.1	2.1	0.05	49	38.70	<0.01	0.15
CC29796		65.7	2.55	4.83	0.09	0.06	0.25	0.041	0.13	11.4	8.4	0.20	122	27.30	0.01	0.55
CC29797		27.4	1.85	4.47	0.06	0.04	0.16	0.029	0.07	10.8	8.4	0.23	81	9.03	0.01	0.55
CC29798		24.0	2.29	5.19	0.05	0.04	0.13	0.034	0.08	11.5	12.2	0.25	75	10.15	0.01	0.66
CC29799		18.0	0.92	0.94	0.08	0.03	0.18	0.016	0.04	2.3	0.9	0.06	24	16.95	0.02	0.20
CC29800		48.0	1.74	3.32	0.09	0.15	0.25	0.031	0.07	9.0	7.6	0.24	194	19.30	0.01	0.45
CC29801		76.4	2.31	3.49	0.12	0.14	0.45	0.033	0.09	13.8	7.5	0.36	173	49.90	0.01	0.44
CC29802		33.5	1.53	2.01	0.08	0.09	0.21	0.018	0.05	21.7	4.5	0.25	96	27.00	0.01	0.29
CC29803		34.8	2.10	2.78	0.07	0.12	0.20	0.022	0.05	11.6	6.3	0.22	257	41.50	0.01	0.46
CC29804		35.3	1.83	3.87	0.05	0.03	0.14	0.020	0.06	6.8	5.9	0.15	83	22.20	<0.01	0.28

Comments: Interference: Ca>10% on ICP-MS As,ICP-AES results shown. Gold determinations by ME-MS41 are semi-quantitative due to the small sample weight used (0.5g).

ALS Chemex
EXCELLENCE IN ANALYTICAL CHEMISTRY
ALS Canada Ltd.
212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: STRATEGIC METALS LTD.
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO

Finalized Date: 9-JUL-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07067610

Sample Description	Method	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41
	Analyte	Ni	P	Pb	Rb	Re	S	Sb	Sc	Se	Sn	Sr	Ta	Te	Th	Ti
	Units	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%
	LOR	0.2	10	0.2	0.1	0.001	0.01	0.05	0.1	0.2	0.2	0.2	0.01	0.01	0.2	0.005
CC29760		254.0	830	13.0	16.9	0.045	0.08	13.40	6.0	14.5	0.8	65.8	0.01	0.15	4.0	0.026
CC29761		59.4	540	10.9	10.3	0.005	0.16	1.76	5.5	3.0	0.2	528.0	<0.01	0.05	4.5	<0.005
CC29762		85.1	660	15.4	9.5	0.010	0.18	2.63	6.1	4.9	0.2	105.0	<0.01	0.08	5.8	<0.005
CC29765		41.9	1510	21.9	9.0	0.004	0.10	3.79	2.9	3.4	0.3	73.2	<0.01	0.06	1.9	0.014
CC29766		41.2	1550	21.4	9.3	0.005	0.10	3.79	2.9	3.4	0.3	73.6	<0.01	0.05	1.9	0.013
CC29767		50.8	2140	31.2	11.9	0.006	0.11	3.63	3.6	3.3	0.4	73.1	<0.01	0.08	3.0	0.008
CC29771		19.7	610	13.3	13.6	0.001	0.01	0.75	3.8	0.8	0.5	29.8	<0.01	0.04	4.0	0.014
CC29772		22.0	480	13.9	12.3	0.001	<0.01	0.85	4.6	0.9	0.5	24.8	<0.01	0.04	5.2	0.013
CC29773		25.7	640	14.6	14.4	0.001	0.01	0.95	5.2	1.2	0.5	25.5	<0.01	0.05	5.7	0.015
CC29774		21.8	460	13.5	13.4	0.001	0.01	1.00	4.7	0.9	0.5	21.9	<0.01	0.04	5.5	0.017
CC29775		21.5	490	13.3	11.9	0.001	0.01	0.64	4.2	0.9	0.5	27.0	<0.01	0.03	4.4	0.011
CC29776		22.4	510	12.7	12.0	0.001	<0.01	0.80	4.6	0.9	0.5	19.7	<0.01	0.04	5.3	0.013
CC29777		25.6	520	13.6	13.4	0.001	<0.01	0.78	4.7	1.1	0.5	24.3	<0.01	0.05	5.2	0.011
CC29778		21.7	450	12.4	11.4	0.001	0.01	0.62	4.1	1.0	0.4	22.4	<0.01	0.03	4.7	0.012
CC29779		19.9	440	12.4	11.7	0.001	<0.01	0.71	4.0	1.1	0.4	18.4	<0.01	0.04	5.2	0.013
CC29780		21.5	460	13.4	13.7	0.001	0.01	0.65	4.1	1.3	0.5	22.7	<0.01	0.04	4.6	0.013
CC29781		23.3	530	12.9	12.7	0.001	0.01	0.69	4.7	1.3	0.5	22.5	<0.01	0.05	5.2	0.012
CC29782		15.0	480	8.4	10.1	<0.001	0.02	0.35	2.7	0.8	0.3	21.3	<0.01	0.03	2.8	0.008
CC29783		23.6	460	12.8	13.1	0.001	0.01	0.61	4.2	1.3	0.4	22.4	<0.01	0.04	5.2	0.011
CC29784		19.5	370	11.1	10.7	0.001	0.02	0.53	3.8	1.2	0.3	27.4	<0.01	0.05	4.3	0.008
CC29785		17.1	410	11.7	11.8	0.001	0.02	0.50	3.7	1.3	0.4	22.5	<0.01	0.03	4.5	0.009
CC29786		17.9	460	10.6	11.5	0.001	0.02	0.46	3.5	1.4	0.4	24.8	<0.01	0.04	4.4	0.008
CC29787		21.6	430	12.5	10.7	0.001	0.04	1.02	3.2	1.9	0.3	38.3	<0.01	0.05	3.7	0.006
CC29788		23.5	360	12.3	12.2	0.002	0.03	0.75	4.0	1.6	0.4	36.5	<0.01	0.04	4.2	0.008
CC29789		22.6	660	12.0	11.7	0.002	0.07	1.61	4.1	3.4	0.5	44.5	<0.01	0.05	4.1	0.009
CC29790		29.7	530	12.6	13.2	0.001	0.06	1.83	4.3	2.0	0.5	39.3	<0.01	0.06	4.1	0.009
CC29791		224.0	730	11.1	10.2	0.003	0.09	9.73	5.4	3.4	0.8	82.1	0.01	0.10	4.3	0.009
CC29792		340.0	1100	16.2	14.2	0.007	0.03	32.30	6.6	6.2	0.9	147.5	0.01	0.21	4.6	0.008
CC29793		203.0	270	10.0	6.5	0.016	0.03	4.86	4.0	4.2	0.4	28.1	<0.01	0.10	1.8	<0.005
CC29794		264.0	260	8.1	7.0	0.007	0.01	4.12	4.8	3.5	0.3	22.9	<0.01	0.08	3.1	<0.005
CC29795		84.3	350	8.6	8.4	0.011	0.02	2.70	3.7	3.6	0.4	62.7	<0.01	0.10	2.1	<0.005
CC29796		57.5	490	11.7	11.6	0.002	0.18	4.59	4.2	5.9	0.6	33.7	<0.01	0.12	2.8	0.009
CC29797		20.4	460	9.9	8.4	0.004	0.04	1.87	3.2	3.5	0.5	20.6	<0.01	0.07	2.4	0.010
CC29798		16.4	390	11.4	11.1	0.002	0.02	1.73	3.2	2.7	0.5	13.7	<0.01	0.05	2.7	0.011
CC29799		19.1	1260	3.9	3.0	0.061	0.16	12.90	1.8	17.0	0.2	29.2	<0.01	0.10	0.2	0.005
CC29800		127.0	520	10.0	8.4	0.017	0.12	5.37	4.3	10.1	0.5	95.1	<0.01	0.13	1.9	0.007
CC29801		265.0	500	12.5	7.9	0.006	0.08	8.86	4.8	9.9	0.6	100.5	0.01	0.13	2.5	0.009
CC29802		159.0	620	7.0	5.3	0.004	0.15	2.19	2.5	4.6	0.3	144.0	<0.01	0.06	0.7	0.007
CC29803		129.0	360	10.4	7.1	0.003	0.08	3.87	3.4	3.9	0.5	88.2	<0.01	0.07	2.4	0.010
CC29804		34.1	440	12.5	10.2	0.001	<0.01	13.10	2.8	2.5	0.5	23.2	<0.01	0.06	2.1	0.008

Comments: Interference: Ca>10% on ICP-MS As,ICP-AES results shown. Gold determinations by ME-MS41 are semi-quantitative due to the small sample weight used (0.5g).

ALS Chemex
EXCELLENCE IN ANALYTICAL CHEMISTRY
ALS Canada Ltd.
212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: STRATEGIC METALS LTD.
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO

Finalized Date: 9-JUL-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07067610

Sample Description	Method	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41
	Analyte	Ti	U	V	W	Y	Zn	Zr
	Units	ppm	ppm	ppm	ppm	ppm	ppm	ppm
	LOR	0.02	0.05	1	0.05	0.05	2	0.5
CC29760		1.33	13.45	777	0.39	45.60	1120	5.8
CC29761		0.18	1.14	40	0.05	15.90	299	2.1
CC29762		0.17	1.61	50	0.05	17.25	454	2.9
CC29765		0.25	2.63	79	0.18	13.15	451	2.6
CC29766		0.24	2.70	82	0.15	13.40	451	2.5
CC29767		0.25	2.90	92	0.09	16.55	438	2.6
CC29771		0.18	1.06	54	0.09	7.84	94	1.0
CC29772		0.17	1.13	53	0.08	10.55	99	2.2
CC29773		0.18	1.24	58	0.12	12.45	97	2.6
CC29774		0.16	1.42	57	0.13	9.91	95	2.7
CC29775		0.15	1.27	52	0.12	9.08	91	1.1
CC29776		0.15	1.23	53	0.10	9.32	95	2.1
CC29777		0.15	1.49	48	0.12	10.70	90	1.8
CC29778		0.15	1.22	45	0.10	8.13	87	1.4
CC29779		0.15	1.34	46	0.09	8.16	85	1.7
CC29780		0.15	1.30	48	0.11	7.71	85	1.1
CC29781		0.16	1.23	46	0.08	9.96	85	1.9
CC29782		0.10	0.69	34	0.06	5.02	63	0.7
CC29783		0.15	0.98	40	0.10	7.65	90	1.9
CC29784		0.13	1.02	32	0.07	7.68	64	1.2
CC29785		0.13	0.80	32	0.08	6.66	64	1.3
CC29786		0.13	0.84	33	0.07	6.88	70	1.4
CC29787		0.14	1.39	45	0.05	9.02	94	1.1
CC29788		0.16	1.52	45	0.06	9.29	95	1.1
CC29789		0.18	2.87	88	0.08	10.95	143	1.3
CC29790		0.22	2.84	96	0.08	10.80	125	1.0
CC29791		1.44	8.73	582	0.26	32.70	681	6.1
CC29792		1.71	9.02	1075	0.26	40.30	2530	6.7
CC29793		0.79	3.39	276	0.17	20.30	554	2.4
CC29794		0.75	4.52	175	0.15	30.30	971	6.6
CC29795		0.93	7.90	199	0.13	17.55	279	1.2
CC29796		2.00	4.84	198	0.15	11.85	148	1.6
CC29797		0.85	2.41	111	0.11	5.90	71	1.0
CC29798		0.75	2.00	121	0.27	3.99	68	1.0
CC29799		0.53	2.47	81	0.05	4.09	33	0.8
CC29800		1.69	5.14	297	0.13	15.50	440	4.6
CC29801		1.63	5.61	425	0.27	29.80	730	5.0
CC29802		0.88	12.00	168	0.13	24.50	187	3.6
CC29803		0.67	8.24	215	0.16	20.10	269	4.4
CC29804		0.46	3.14	391	0.12	6.02	374	1.0

Comments: Interference: Ca>10% on ICP-MS As,ICP-AES results shown. Gold determinations by ME-MS41 are semi-quantitative due to the small sample weight used (0.5g).

ALS Chemex

EXCELLENCE IN ANALYTICAL CHEMISTRY

ALS Canada Ltd.

212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: STRATEGIC METALS LTD.
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO

Finalized Date: 9-JUL-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07067610

Sample Description	Method / Analyte / Units / LOR	WEI-21 Recvd Wt. kg 0.02	ME-MS41 Ag ppm 0.01	ME-MS41 Al % 0.01	ME-MS41 As ppm 0.1	ME-MS41 Au ppm 0.2	ME-MS41 B ppm 10	ME-MS41 Ba ppm 10	ME-MS41 Be ppm 0.05	ME-MS41 Bi ppm 0.01	ME-MS41 Ca % 0.01	ME-MS41 Cd ppm 0.01	ME-MS41 Ce ppm 0.02	ME-MS41 Co ppm 0.1	ME-MS41 Cr ppm 1	ME-MS41 Cs ppm 0.05
CC29805		0.10	0.91	0.80	10.3	<0.2	<10	5530	0.60	0.17	0.21	0.63	13.80	8.4	26	0.52
CC29806		0.10	0.49	0.61	5.6	<0.2	<10	3800	0.39	0.14	1.22	0.40	11.90	6.0	13	0.35
CC29807		0.10	0.61	0.64	3.4	<0.2	10	2410	0.30	0.06	2.99	0.36	8.95	3.6	12	0.64
CC29808		0.10	0.93	1.27	4.3	<0.2	<10	4940	0.54	0.14	0.56	0.64	18.65	4.9	20	0.84
CC29809		0.12	0.25	1.77	10.2	<0.2	<10	4040	1.00	0.20	0.08	0.34	37.10	14.7	31	0.76
CC29851		0.16	0.37	0.77	6.7	<0.2	<10	440	0.39	0.17	0.12	1.32	21.50	3.4	17	0.49
CC29852		0.14	0.41	0.69	10.0	<0.2	<10	250	0.17	0.15	0.11	0.20	8.97	0.8	16	0.40
CC29853		0.22	0.39	0.35	6.5	<0.2	<10	500	0.32	0.17	0.55	0.26	6.30	0.3	10	0.55
CC29854		0.26	0.19	0.31	14.0	<0.2	<10	550	0.48	0.16	0.17	0.48	6.34	2.3	9	0.24
CC29855		0.22	0.15	0.15	2.8	<0.2	<10	110	0.12	0.12	0.02	0.12	3.45	0.1	6	0.42
CC29856		0.22	0.50	0.41	16.1	<0.2	<10	150	0.35	0.17	0.01	0.15	8.37	0.5	12	0.60
CC29857		0.26	0.40	0.29	20.1	<0.2	<10	210	0.21	0.13	0.01	0.20	6.99	0.3	12	0.50
CC29858		0.24	2.32	0.65	123.0	<0.2	<10	420	0.32	0.30	0.01	0.28	12.20	0.7	36	0.76
CC29859		0.24	1.37	0.55	8.2	<0.2	<10	110	0.26	0.14	<0.01	0.20	6.11	0.4	17	0.51
CC29860		0.24	0.14	0.45	13.2	<0.2	<10	350	0.47	0.13	0.18	0.98	12.75	3.2	8	0.56
CC29861		0.20	0.60	0.70	23.8	<0.2	<10	490	0.67	0.15	0.65	5.80	16.30	5.0	18	0.56
CC29862		0.16	1.08	0.87	33.8	<0.2	<10	610	0.84	0.14	1.69	12.15	19.20	5.9	28	0.60
CC29863		0.18	1.39	0.77	57.0	<0.2	<10	550	0.80	0.14	2.12	28.80	26.40	6.6	40	0.66
CC29864		0.22	1.49	1.38	192.5	<0.2	<10	380	0.83	0.28	0.55	24.50	17.95	11.2	90	1.37
CC29865		0.26	7.80	0.79	44	<0.2	<10	760	1.14	0.12	14.70	51.20	26.10	5.6	80	0.74
CC29866		0.20	5.41	0.57	105.0	<0.2	10	1090	0.86	0.25	4.81	43.30	17.80	12.3	52	1.84
CC29867		0.22	5.00	0.92	87.1	<0.2	<10	590	1.66	0.14	3.68	68.30	29.60	5.5	105	0.89
CC29868		0.16	4.77	0.63	80.6	<0.2	<10	500	0.87	0.11	3.87	93.40	16.90	4.8	55	0.64
CC29869		0.12	0.77	0.43	24.7	<0.2	<10	230	0.31	0.09	1.52	11.05	10.15	1.6	26	0.85
CC29870		0.08	1.24	0.79	17.6	<0.2	<10	3130	0.52	0.18	1.23	4.96	20.90	4.6	24	0.71
CC29871		0.14	0.86	2.29	68.5	<0.2	<10	800	0.60	0.26	0.05	0.52	16.15	6.3	46	1.64
CC29872		0.18	0.88	1.17	54.9	<0.2	<10	630	0.34	0.27	0.05	0.62	18.80	4.1	32	1.33
CC29873		0.08	0.58	0.73	16.4	<0.2	<10	600	0.24	0.17	0.28	0.44	11.75	1.8	20	1.31
CC29874		0.12	0.49	0.97	19.2	<0.2	<10	580	0.28	0.16	0.27	0.34	15.50	2.4	21	1.16
CC29875		0.16	0.20	1.53	16.8	<0.2	<10	330	0.38	0.22	0.09	0.25	24.00	3.9	26	1.09
CC29876		0.14	0.38	1.51	16.2	<0.2	<10	370	0.45	0.22	0.12	0.25	20.60	3.3	26	1.24
CC29877		0.10	0.76	1.26	30.7	<0.2	<10	1070	0.82	0.19	1.59	8.24	21.40	11.8	38	0.98
CC29878		0.14	0.49	0.57	26.2	<0.2	<10	1060	0.90	0.15	3.45	9.00	25.40	7.6	31	0.61
CC29879		0.06	0.41	1.09	18.2	<0.2	<10	820	0.46	0.19	0.96	0.53	20.10	3.5	24	0.98
CC29880		0.14	0.31	1.09	12.6	<0.2	<10	2250	0.59	0.20	0.31	0.53	22.00	8.7	25	0.66
CC29881		0.10	0.27	0.76	10.6	<0.2	<10	3310	0.56	0.18	1.19	1.56	19.15	9.4	17	0.42
CC29882		0.14	0.44	0.68	8.3	<0.2	<10	3190	0.49	0.14	1.78	2.47	21.70	9.9	16	0.48
CC29883		0.10	0.49	0.73	5.3	<0.2	<10	3610	0.52	0.13	1.87	1.51	17.70	7.2	16	0.52
CC29884		0.10	0.32	1.34	10.8	<0.2	<10	740	0.99	0.16	0.27	1.28	23.60	6.5	26	0.85
CC29885		0.16	0.34	0.99	26.1	<0.2	<10	770	1.12	0.19	0.60	2.51	26.30	9.6	31	0.72

Comments: Interference: Ca>10% on ICP-MS As,ICP-AES results shown. Gold determinations by ME-MS41 are semi-quantitative due to the small sample weight used (0.5g).

ALS Chemex

EXCELLENCE IN ANALYTICAL CHEMISTRY

ALS Canada Ltd.

212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: STRATEGIC METALS LTD.
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO

Finalized Date: 9-JUL-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07067610

Sample Description	Method	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41
	Analyte	Cu	Fe	Ga	Ge	Hf	Hg	In	K	La	Li	Mg	Mn	Mo	Na	Nb
	Units	ppm	%	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	%	ppm	ppm	%	ppm
	LOR	0.2	0.01	0.05	0.05	0.02	0.01	0.005	0.01	0.2	0.1	0.01	5	0.05	0.01	0.05
CC29805		54.6	3.30	2.35	0.07	0.06	0.25	0.030	0.05	6.6	4.2	0.12	234	4.98	<0.01	0.15
CC29806		24.8	1.72	1.61	0.06	0.08	0.12	0.020	0.07	6.1	2.8	0.20	110	2.87	<0.01	0.07
CC29807		19.2	0.97	1.52	0.06	0.08	0.17	0.012	0.04	5.4	3.5	0.57	145	1.54	<0.01	0.16
CC29808		25.8	1.62	4.12	0.06	0.04	0.12	0.021	0.06	9.7	5.5	0.20	60	1.74	<0.01	0.28
CC29809		39.3	3.31	4.74	0.10	0.12	0.10	0.032	0.09	18.9	13.5	0.35	353	1.84	<0.01	0.39
CC29851		30.1	1.09	2.87	0.07	0.05	0.09	0.020	0.05	10.8	7.3	0.19	55	6.04	<0.01	0.35
CC29852		18.4	1.20	2.26	0.05	0.02	0.18	0.014	0.05	5.0	2.8	0.10	22	11.85	<0.01	0.17
CC29853		27.7	0.36	2.32	<0.05	0.02	0.20	0.014	0.04	3.3	0.9	0.05	6	4.76	<0.01	<0.05
CC29854		35.0	0.71	1.72	<0.05	0.04	0.15	0.017	0.06	3.0	0.9	0.02	67	11.95	<0.01	<0.05
CC29855		30.4	0.14	0.89	<0.05	<0.02	0.04	0.006	0.04	2.0	0.3	0.01	<5	6.13	<0.01	<0.05
CC29856		43.9	0.76	2.27	0.06	0.02	0.09	0.024	0.06	4.8	1.2	0.03	15	22.80	<0.01	0.09
CC29857		50.8	0.89	2.24	0.07	<0.02	0.04	0.021	0.09	4.2	0.6	0.01	<5	29.40	<0.01	0.07
CC29858		46.2	2.84	4.74	0.17	<0.02	0.13	0.056	0.21	7.6	2.0	0.04	20	74.80	<0.01	0.10
CC29859		27.5	0.44	2.01	<0.05	<0.02	0.07	0.009	0.07	4.3	1.2	0.03	8	7.16	<0.01	0.07
CC29860		29.0	1.21	1.48	0.08	0.03	0.06	0.016	0.07	6.6	1.3	0.03	28	22.60	<0.01	<0.05
CC29861		57.4	1.64	2.47	0.08	0.07	0.18	0.026	0.07	9.3	4.1	0.12	72	26.40	<0.01	0.17
CC29862		67.6	1.67	3.10	0.11	0.09	0.30	0.025	0.05	14.0	5.9	0.19	173	19.25	<0.01	0.30
CC29863		74.8	1.64	2.98	0.20	0.09	0.34	0.024	0.06	20.9	3.6	0.15	282	44.40	<0.01	0.21
CC29864		109.0	2.73	7.26	0.54	0.05	0.46	0.058	0.08	12.5	7.1	0.13	153	95.10	<0.01	0.29
CC29865		195.0	0.99	4.20	0.25	0.13	1.66	0.024	0.08	37.4	4.1	0.14	85	34.80	<0.01	0.10
CC29866		156.0	2.19	3.73	0.20	0.12	1.34	0.032	0.13	11.2	2.7	1.70	130	104.50	0.01	0.09
CC29867		160.0	1.37	4.93	0.25	0.11	0.42	0.023	0.08	30.9	5.0	0.14	165	71.20	<0.01	0.21
CC29868		199.0	1.33	3.34	0.20	0.08	0.68	0.020	0.05	18.4	2.2	0.09	127	63.80	<0.01	0.14
CC29869		44.3	0.80	2.34	0.08	0.02	0.21	0.016	0.03	7.1	0.9	0.04	23	21.80	<0.01	0.11
CC29870		51.6	1.58	2.41	0.10	0.09	0.36	0.027	0.06	11.5	5.1	0.16	124	6.65	<0.01	0.16
CC29871		84.5	3.53	6.15	0.11	0.06	0.14	0.063	0.16	8.6	13.1	0.24	146	82.30	<0.01	0.60
CC29872		32.1	3.45	5.95	0.12	0.02	0.10	0.039	0.18	10.5	8.0	0.20	93	75.40	<0.01	0.52
CC29873		23.6	1.30	3.79	0.06	<0.02	0.44	0.019	0.10	6.6	2.8	0.09	29	17.10	<0.01	0.29
CC29874		23.9	1.55	4.28	0.06	0.02	0.30	0.019	0.08	8.2	4.4	0.14	34	12.10	<0.01	0.36
CC29875		20.1	2.62	5.62	0.07	0.02	0.16	0.027	0.08	12.5	11.3	0.29	92	21.20	<0.01	0.57
CC29876		22.4	2.48	5.47	0.06	0.02	0.14	0.025	0.07	10.7	11.1	0.24	56	13.50	<0.01	0.56
CC29877		50.1	2.26	4.06	0.11	0.10	0.29	0.033	0.07	11.4	11.1	0.26	412	31.60	<0.01	0.50
CC29878		58.9	1.95	2.36	0.11	0.11	0.30	0.025	0.05	14.5	4.7	0.44	166	48.20	<0.01	0.19
CC29879		22.2	1.81	4.03	0.07	0.03	0.16	0.024	0.06	10.6	8.7	0.26	96	9.49	<0.01	0.42
CC29880		39.9	2.81	3.43	0.07	0.04	0.13	0.030	0.09	11.5	9.1	0.20	161	6.77	<0.01	0.30
CC29881		30.1	1.98	2.40	0.08	0.11	0.13	0.028	0.07	10.0	6.1	0.30	264	8.13	0.03	0.35
CC29882		27.2	1.64	2.32	0.08	0.10	0.12	0.024	0.06	9.6	4.4	0.36	288	7.81	0.03	0.30
CC29883		24.2	1.65	2.13	0.08	0.10	0.14	0.021	0.05	9.4	5.3	0.41	270	4.20	0.04	0.32
CC29884		37.6	1.68	3.71	0.08	0.06	0.17	0.025	0.05	12.5	9.4	0.18	98	13.85	0.01	0.43
CC29885		52.9	2.33	3.77	0.10	0.07	0.24	0.029	0.05	13.9	8.3	0.16	175	29.10	0.01	0.41

Comments: Interference: Ca>10% on ICP-MS As,ICP-AES results shown. Gold determinations by ME-MS41 are semi-quantitative due to the small sample weight used (0.5g).

ALS Chemex

EXCELLENCE IN ANALYTICAL CHEMISTRY

ALS Canada Ltd.

212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: STRATEGIC METALS LTD.
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO

Finalized Date: 9-JUL-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07067610

Sample Description	Method	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41
	Analyte	Ni	P	Pb	Rb	Re	S	Sb	Sc	Se	Sn	Sr	Ta	Te	Th	Ti
	Units	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%
	LOR	0.2	10	0.2	0.1	0.001	0.01	0.05	0.1	0.2	0.2	0.2	0.01	0.01	0.2	0.005
CC29805		44.0	370	11.7	6.6	0.001	0.04	1.58	5.0	3.2	0.3	56.2	<0.01	0.05	2.1	<0.005
CC29806		19.2	620	8.4	6.1	0.002	0.11	0.73	3.1	3.1	0.3	99.6	<0.01	0.05	1.8	<0.005
CC29807		27.5	810	4.4	4.2	0.002	0.17	0.83	2.7	3.5	0.2	222.0	0.01	0.03	0.8	0.006
CC29808		27.8	410	10.9	6.3	<0.001	0.01	0.73	3.5	1.8	0.6	46.7	<0.01	0.04	2.2	0.007
CC29809		42.0	300	12.4	9.1	<0.001	<0.01	0.97	7.9	1.6	0.5	15.8	0.01	0.04	6.3	0.015
CC29851		23.2	340	9.7	6.9	0.002	<0.01	5.23	4.0	4.8	0.4	19.1	<0.01	0.09	4.1	0.015
CC29852		7.1	290	8.8	5.5	0.006	0.01	2.17	1.7	6.1	0.4	14.2	<0.01	0.09	1.2	0.007
CC29853		9.3	240	10.4	4.8	0.008	0.02	1.26	1.9	3.5	0.5	51.6	<0.01	0.08	0.7	<0.005
CC29854		14.8	180	9.6	3.9	0.007	0.07	1.34	2.4	4.3	0.4	65.0	<0.01	0.11	1.4	<0.005
CC29855		4.5	40	7.2	4.0	0.012	<0.01	1.75	1.3	2.2	0.3	6.8	<0.01	0.05	1.1	<0.005
CC29856		9.9	180	10.5	6.8	0.008	0.04	7.61	2.5	7.1	0.4	25.0	<0.01	0.16	1.5	<0.005
CC29857		9.5	640	10.0	7.0	0.010	0.13	9.03	2.5	10.4	0.4	24.4	<0.01	0.13	0.7	<0.005
CC29858		8.3	1210	24.3	15.3	0.004	0.50	25.10	7.4	35.7	0.8	63.0	<0.01	0.64	2.2	<0.005
CC29859		5.4	80	9.0	8.6	0.003	<0.01	18.05	1.5	3.9	0.4	5.2	<0.01	0.16	1.0	<0.005
CC29860		67.2	150	8.6	7.4	0.010	<0.01	2.29	2.5	11.3	0.3	24.4	<0.01	0.05	1.6	<0.005
CC29861		155.0	390	9.9	7.5	0.008	<0.01	5.59	4.0	4.7	0.4	47.3	<0.01	0.09	2.1	0.005
CC29862		184.5	790	9.3	7.2	0.009	0.04	9.64	3.6	11.5	0.5	71.2	<0.01	0.10	1.2	0.008
CC29863		220.0	1330	12.0	6.2	0.017	0.10	22.30	3.4	31.5	0.4	90.5	0.01	0.17	0.7	0.009
CC29864		881.0	1010	22.1	12.7	0.024	0.03	59.30	4.5	124.0	0.9	36.5	<0.01	0.44	1.6	0.008
CC29865		251.0	750	14.8	9.8	0.010	0.07	43.00	4.0	40.5	0.5	562.0	0.01	0.18	0.6	0.006
CC29866		476.0	920	20.2	13.0	0.018	0.11	44.40	7.0	25.4	0.8	195.0	<0.01	0.21	2.8	0.006
CC29867		355.0	1430	13.7	9.6	0.012	0.16	52.30	2.9	30.5	0.4	105.0	0.01	0.24	0.4	0.006
CC29868		492.0	1340	11.3	5.8	0.020	0.17	37.30	3.2	25.7	0.4	114.0	0.01	0.19	0.3	0.006
CC29869		147.5	680	6.5	4.0	0.014	0.09	9.79	2.6	13.3	0.5	52.6	<0.01	0.11	0.6	0.009
CC29870		63.2	890	11.6	9.4	0.054	0.15	3.68	3.2	11.2	0.4	106.0	<0.01	0.07	1.4	0.005
CC29871		31.2	630	17.6	18.4	0.001	0.30	15.70	5.4	15.8	0.8	53.7	<0.01	0.23	3.2	0.012
CC29872		36.2	730	19.4	15.8	<0.001	0.32	16.40	3.0	15.8	0.8	65.5	<0.01	0.24	2.6	0.014
CC29873		21.1	600	10.8	13.8	0.009	0.10	6.39	2.4	6.0	0.6	48.3	<0.01	0.09	1.6	0.006
CC29874		18.5	620	8.7	10.9	0.009	0.05	4.49	2.7	5.3	0.6	36.8	<0.01	0.08	1.6	0.008
CC29875		17.4	340	11.7	12.8	0.001	<0.01	3.32	3.2	4.2	0.6	17.1	<0.01	0.08	3.3	0.014
CC29876		16.8	420	11.1	13.4	0.003	<0.01	2.70	3.2	4.2	0.6	16.9	<0.01	0.07	2.5	0.009
CC29877		156.5	540	11.7	10.7	0.005	0.05	5.85	4.3	8.6	0.6	66.8	<0.01	0.11	1.9	0.008
CC29878		203.0	430	11.1	6.5	0.005	0.06	3.86	5.0	7.6	0.5	107.0	<0.01	0.09	3.1	0.008
CC29879		26.9	510	11.7	11.6	0.014	0.06	2.57	3.1	4.1	0.5	49.1	<0.01	0.05	2.0	0.011
CC29880		34.2	660	13.9	10.2	0.003	0.01	1.89	4.1	2.9	0.5	38.1	<0.01	0.06	3.5	0.007
CC29881		43.4	520	11.3	6.9	0.003	0.12	2.20	3.9	3.1	0.3	76.0	<0.01	0.06	2.3	0.008
CC29882		39.5	450	11.4	6.6	0.001	0.11	2.64	3.8	3.2	0.3	104.5	<0.01	0.06	1.8	0.006
CC29883		36.2	590	8.4	6.3	0.001	0.12	1.40	3.7	3.1	0.3	124.5	<0.01	0.05	1.4	0.007
CC29884		80.2	510	10.8	9.5	0.008	0.05	1.42	3.5	4.3	0.5	24.6	<0.01	0.07	2.6	0.007
CC29885		109.0	490	14.0	9.9	0.006	0.04	2.91	4.1	4.8	0.7	53.9	0.01	0.10	3.2	0.007

Comments: Interference: Ca>10% on ICP-MS As,ICP-AES results shown. Gold determinations by ME-MS41 are semi-quantitative due to the small sample weight used (0.5g).

ALS Chemex

EXCELLENCE IN ANALYTICAL CHEMISTRY

ALS Canada Ltd.

212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: STRATEGIC METALS LTD.
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO

Finalized Date: 9-JUL-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07067610

Sample Description	Method / Analyte / Units / LOR	ME-MS41 Tl ppm 0.02	ME-MS41 U ppm 0.05	ME-MS41 V ppm 1	ME-MS41 W ppm 0.05	ME-MS41 Y ppm 0.05	ME-MS41 Zn ppm 2	ME-MS41 Zr ppm 0.5
CC29805		0.14	2.06	50	0.19	15.60	144	1.6
CC29806		0.05	1.92	46	<0.05	10.80	51	2.0
CC29807		0.07	3.47	28	<0.05	10.90	45	2.4
CC29808		0.13	1.89	58	0.22	12.10	81	0.8
CC29809		0.12	1.33	68	0.11	23.40	125	4.5
CC29851		0.66	3.29	139	0.13	9.18	91	2.4
CC29852		0.79	1.88	116	0.12	2.36	35	0.8
CC29853		0.96	3.84	57	0.09	3.67	10	1.0
CC29854		0.78	2.27	62	0.15	7.36	31	2.0
CC29855		0.99	3.86	42	0.09	2.30	5	0.6
CC29856		1.64	6.07	211	0.15	3.87	26	1.4
CC29857		1.74	9.22	155	0.23	4.57	27	<0.5
CC29858		4.02	7.64	557	0.35	8.69	31	0.9
CC29859		0.92	2.74	295	0.11	3.68	14	0.7
CC29860		1.03	1.56	99	0.09	13.10	106	1.1
CC29861		1.26	3.49	215	0.19	18.75	499	2.8
CC29862		2.08	5.17	287	0.17	27.80	1180	3.0
CC29863		2.58	8.80	521	0.23	44.30	1800	2.7
CC29864		10.80	7.38	1135	0.46	42.30	3930	1.9
CC29865		4.65	2.72	1065	0.34	64.80	4660	3.6
CC29866		4.68	13.25	1275	0.35	42.60	3680	4.8
CC29867		3.95	6.60	1260	0.29	70.60	4510	2.7
CC29868		4.37	16.50	599	0.25	54.90	5010	2.4
CC29869		1.74	5.32	178	0.13	11.25	642	1.0
CC29870		0.78	7.26	266	0.14	19.70	334	2.5
CC29871		4.60	6.47	582	0.26	5.36	95	2.2
CC29872		4.40	2.47	461	0.28	4.98	114	0.9
CC29873		2.01	2.42	115	0.11	3.92	65	0.8
CC29874		1.70	2.35	102	0.12	5.02	52	0.8
CC29875		1.22	1.40	143	0.16	4.32	87	1.0
CC29876		1.13	1.67	140	0.17	4.79	66	0.9
CC29877		1.66	9.64	373	0.19	22.70	508	3.0
CC29878		1.14	6.64	266	0.25	33.50	416	6.1
CC29879		1.11	3.75	188	0.20	8.96	83	1.1
CC29880		0.17	2.30	74	0.09	13.60	124	1.2
CC29881		0.13	3.01	64	0.08	14.70	157	2.7
CC29882		0.15	3.00	80	0.07	15.70	155	2.5
CC29883		0.14	3.14	49	0.07	15.10	93	2.3
CC29884		0.60	8.42	132	0.14	19.95	170	1.7
CC29885		0.71	9.37	271	0.23	25.10	236	2.3

Comments: Interference: Ca>10% on ICP-MS As,ICP-AES results shown. Gold determinations by ME-MS41 are semi-quantitative due to the small sample weight used (0.5g).

ALS Chemex

EXCELLENCE IN ANALYTICAL CHEMISTRY

ALS Canada Ltd.

212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: STRATEGIC METALS LTD.
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO

Finalized Date: 9-JUL-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07067610

Sample Description	Method	WEI-21	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41
	Analyte	Recvd Wt.	Ag	Al	As	Au	B	Ba	Be	Bi	Ca	Cd	Ce	Co	Cr	Cs
	Units	kg	ppm	%	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppm	ppm	ppm
	LOR	0.02	0.01	0.01	0.1	0.2	10	10	0.05	0.01	0.01	0.01	0.02	0.1	1	0.05
CC29886		0.12	0.62	1.22	22.1	<0.2	<10	990	0.90	0.23	0.36	2.73	26.20	15.9	35	0.97
CC29887		0.14	0.28	1.29	13.0	<0.2	<10	400	0.33	0.21	0.11	0.17	20.50	4.6	22	0.95
CC29901		0.02	0.98	0.70	12.5	<0.2	<10	1590	0.60	0.17	1.15	3.76	14.40	1.9	14	0.73
CC29902		0.12	0.09	0.81	16.5	<0.2	<10	210	0.16	0.23	0.04	0.28	14.55	2.4	19	0.80
CC29903		0.10	0.22	0.16	8.2	<0.2	<10	210	0.12	0.13	0.01	0.22	3.41	0.1	6	0.33
CC29904		0.10	0.77	1.15	31.1	<0.2	<10	380	0.27	0.28	0.04	0.37	17.30	3.5	29	0.95
CC29905		0.08	0.91	0.83	25.6	<0.2	<10	260	0.22	0.25	0.02	0.22	12.95	2.0	27	0.66
CC29906		0.14	1.47	1.20	42.0	<0.2	<10	410	0.52	0.21	0.03	1.18	18.40	4.5	33	0.90
CC29907		0.12	0.30	1.71	43.1	<0.2	<10	230	0.49	0.27	0.01	0.54	15.00	5.8	36	1.22
CC29908		0.08	0.16	0.90	17.5	<0.2	<10	1880	0.77	0.16	0.26	1.58	20.30	6.4	22	0.56
CC29909		0.08	0.14	0.33	17.6	<0.2	<10	240	0.34	0.13	0.28	1.55	8.61	3.1	10	0.39
CC29910		0.08	0.29	0.41	44.3	<0.2	<10	290	0.56	0.15	0.16	7.10	13.70	6.1	18	0.46
CC29911		0.06	2.77	1.16	241.0	<0.2	<10	550	1.98	0.24	0.63	15.30	25.80	7.7	137	1.00
CC29912		0.10	3.13	1.02	96.3	<0.2	10	2140	0.91	0.23	4.77	34.00	20.50	9.6	57	1.06
CC29913		0.10	2.29	0.88	46.5	<0.2	10	1880	0.93	0.21	1.98	27.80	20.80	7.8	51	0.99
CC29914		0.12	0.79	0.67	36.5	<0.2	<10	4210	0.94	0.18	1.54	10.45	41.50	7.3	42	0.58
CC29915		0.12	1.51	1.44	56.4	<0.2	<10	530	0.47	0.26	0.11	9.78	21.70	6.2	49	1.16
CC29916		0.14	0.38	1.51	55.4	<0.2	<10	180	0.38	0.26	0.03	0.85	17.00	6.6	34	1.22
CC29917		0.12	0.25	1.11	41.2	<0.2	<10	180	0.34	0.24	0.03	0.78	17.00	5.9	25	0.85
CC29918		0.08	0.12	0.61	16.7	<0.2	<10	250	0.23	0.18	0.04	0.42	18.90	3.9	15	0.97
CC29919		0.16	0.32	0.41	19.1	<0.2	<10	670	0.35	0.21	0.21	1.38	14.30	4.4	10	0.62
CC29920		0.10	0.29	0.96	12.7	<0.2	<10	1590	0.63	0.16	0.36	1.80	17.90	5.2	16	0.55
CC29921		0.14	0.62	0.88	23.0	<0.2	<10	260	0.35	0.16	0.03	0.63	14.45	3.1	18	0.53
CC29922		0.16	0.49	0.62	29.8	<0.2	<10	310	0.25	0.19	0.01	0.32	10.55	1.3	16	0.56
CC29923		0.12	0.45	0.40	37.5	<0.2	<10	290	0.09	0.19	0.01	0.13	5.01	0.5	13	0.50
CC29924		0.10	0.22	0.64	12.9	<0.2	<10	220	0.28	0.16	0.02	0.19	9.53	0.9	12	0.58
CC29925		0.14	0.10	0.28	6.5	<0.2	<10	460	0.42	0.17	0.06	0.94	9.57	0.8	10	0.32
CC29926		0.14	0.07	0.30	5.5	<0.2	<10	270	0.23	0.15	0.08	0.91	6.42	0.4	8	0.37
CC29927		0.08	0.59	1.67	41.4	<0.2	<10	1600	0.95	0.18	0.40	1.25	29.50	7.6	32	0.91
CC29951		0.16	0.34	1.44	10.2	<0.2	<10	1570	0.59	0.23	0.63	1.33	30.00	8.2	29	0.85
CC29952		0.14	0.35	1.57	9.6	<0.2	<10	1690	0.69	0.19	1.18	1.28	28.80	7.7	32	0.71
CC29953		0.14	0.26	1.20	11.5	<0.2	<10	960	0.57	0.19	0.24	0.94	24.60	5.4	23	0.82
CC29954		0.04	0.65	0.89	5.9	<0.2	<10	4090	0.31	0.18	0.17	0.34	17.25	4.5	17	0.65
CC29955		0.04	0.48	0.91	10.7	<0.2	<10	3540	0.40	0.15	0.55	2.15	18.30	45.8	22	0.76
CC29956		0.08	1.58	0.66	23.6	<0.2	<10	1680	0.64	0.12	3.34	30.60	20.50	4.8	31	0.59
CC29957		0.08	1.48	1.01	80.4	<0.2	<10	2280	0.94	0.19	2.17	13.30	26.90	8.2	48	0.67
CC29958		0.20	1.83	1.21	49.1	<0.2	10	3350	1.11	0.20	1.44	16.05	31.50	10.9	50	0.80
CC29959		0.16	5.06	0.90	59.4	<0.2	<10	2170	1.02	0.20	1.69	32.50	26.10	8.2	51	0.96
CC29960		0.12	0.62	1.15	11.6	<0.2	<10	1150	0.88	0.16	0.30	6.55	15.95	1.7	32	0.86
CC29961		0.08	1.72	1.15	23.4	<0.2	<10	1790	0.74	0.21	1.06	5.76	15.25	3.4	29	0.84

Comments: Interference: Ca>10% on ICP-MS As,ICP-AES results shown. Gold determinations by ME-MS41 are semi-quantitative due to the small sample weight used (0.5g).

ALS Chemex

EXCELLENCE IN ANALYTICAL CHEMISTRY

ALS Canada Ltd.

212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO

Finalized Date: 9-JUL-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07067610

Sample Description	Method	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41
	Analyte	Cu	Fe	Ga	Ge	Hf	Hg	In	K	La	Li	Mg	Mn	Mo	Na	Nb
	Units	ppm	%	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	%	ppm	ppm	%	ppm
	LOR	0.2	0.01	0.05	0.05	0.02	0.01	0.005	0.01	0.2	0.1	0.01	5	0.05	0.01	0.05
CC29886		48.2	2.41	4.19	0.11	0.06	0.26	0.039	0.05	13.5	9.4	0.16	274	25.60	0.01	0.52
CC29887		13.9	2.20	4.75	0.06	0.05	0.19	0.027	0.06	10.7	12.5	0.23	116	9.53	0.01	0.69
CC29901		52.7	1.42	2.69	0.10	0.04	0.32	0.033	0.06	7.7	1.5	0.12	27	15.50	0.03	0.27
CC29902		11.9	1.66	5.66	0.05	0.03	0.04	0.015	0.05	7.8	4.3	0.09	60	20.60	0.01	0.61
CC29903		22.8	0.49	1.12	<0.05	<0.02	0.03	0.011	0.07	2.2	0.4	0.01	<5	18.10	0.01	0.09
CC29904		21.3	2.86	6.42	0.10	0.03	0.07	0.034	0.11	9.7	6.0	0.15	110	31.60	0.01	0.82
CC29905		23.8	2.52	4.73	0.09	<0.02	0.05	0.031	0.09	7.2	2.8	0.08	51	23.90	0.01	0.67
CC29906		37.6	3.03	4.61	0.11	0.03	0.07	0.042	0.14	10.7	9.9	0.15	113	43.60	0.01	0.49
CC29907		30.4	3.45	6.94	0.08	0.05	0.03	0.038	0.10	7.8	14.1	0.16	91	52.80	0.01	0.71
CC29908		43.0	1.81	3.15	0.08	0.05	0.10	0.027	0.08	11.3	5.1	0.12	88	29.90	0.02	0.30
CC29909		34.0	1.19	1.36	0.05	0.03	0.07	0.020	0.06	5.6	0.8	0.03	24	28.70	0.01	0.10
CC29910		66.0	1.72	1.43	0.13	0.05	0.10	0.032	0.06	9.4	1.2	0.03	45	65.60	0.01	0.10
CC29911		179.0	3.31	6.41	0.40	0.10	0.69	0.045	0.10	22.3	7.0	0.07	66	253.00	0.01	0.24
CC29912		127.0	2.11	4.86	0.17	0.11	0.75	0.034	0.13	12.9	5.9	0.72	111	97.70	0.03	0.29
CC29913		111.5	1.77	4.24	0.13	0.14	0.77	0.035	0.11	13.0	6.0	0.53	85	55.80	0.03	0.38
CC29914		71.6	1.65	3.28	0.11	0.11	0.35	0.028	0.06	22.1	4.5	0.23	257	47.80	0.04	0.30
CC29915		48.9	2.97	7.75	0.11	0.04	0.20	0.030	0.09	11.8	9.4	0.17	148	37.90	0.01	0.69
CC29916		40.9	3.28	6.28	0.11	0.03	0.08	0.041	0.08	8.8	11.1	0.15	147	50.90	0.01	0.72
CC29917		30.0	3.07	5.29	0.09	0.02	0.05	0.029	0.08	8.8	8.3	0.15	122	38.60	0.01	0.75
CC29918		21.3	1.59	4.34	0.06	<0.02	0.04	0.018	0.05	10.0	1.3	0.03	46	23.20	0.01	0.42
CC29919		25.8	2.37	1.78	0.07	0.09	0.10	0.039	0.16	8.5	2.6	0.06	65	30.20	0.02	0.14
CC29920		30.1	2.73	3.05	0.10	0.05	0.12	0.027	0.07	9.3	3.8	0.10	77	24.10	0.02	0.28
CC29921		29.0	1.98	3.55	0.07	0.03	0.05	0.023	0.07	8.0	6.4	0.11	90	15.45	0.01	0.52
CC29922		29.2	1.89	3.58	0.07	0.02	0.06	0.021	0.11	6.5	2.7	0.05	37	30.60	0.01	0.31
CC29923		15.7	1.79	3.41	0.05	<0.02	0.02	0.018	0.13	3.1	0.9	0.02	10	57.70	0.01	0.24
CC29924		26.9	1.36	2.48	0.05	0.02	0.07	0.020	0.07	5.3	1.6	0.04	21	31.00	0.01	0.28
CC29925		57.2	0.52	1.57	<0.05	0.04	0.06	0.016	0.04	5.0	1.3	0.04	18	7.37	0.01	0.14
CC29926		33.4	0.43	1.54	<0.05	<0.02	0.05	0.010	0.03	3.7	0.8	0.03	8	5.77	0.01	0.13
CC29927		40.6	1.92	5.20	0.09	0.08	0.13	0.031	0.08	15.8	14.1	0.44	136	4.46	0.02	0.45
CC29951		36.8	2.42	5.08	0.08	0.08	0.07	0.034	0.09	15.3	13.9	0.37	165	4.05	0.03	0.70
CC29952		34.3	2.12	4.87	0.08	0.10	0.07	0.033	0.09	15.2	13.3	0.39	176	3.99	0.03	0.63
CC29953		24.4	1.70	4.08	0.08	0.08	0.07	0.029	0.06	12.3	11.0	0.22	101	5.24	0.02	0.48
CC29954		17.6	2.42	2.75	0.07	0.07	0.13	0.021	0.07	8.9	6.0	0.16	103	7.81	0.04	0.31
CC29955		20.6	2.82	3.63	0.09	0.05	0.14	0.022	0.05	9.0	5.1	0.12	2050	20.90	0.04	0.31
CC29956		58.7	1.05	2.46	0.11	0.11	0.31	0.019	0.04	15.4	3.5	0.16	93	19.10	0.03	0.34
CC29957		77.1	1.98	4.09	0.15	0.16	0.33	0.029	0.08	18.2	6.9	0.18	138	84.70	0.03	0.43
CC29958		88.1	2.21	4.67	0.15	0.16	0.40	0.031	0.08	22.5	9.2	0.28	178	58.40	0.04	0.46
CC29959		114.0	1.57	3.92	0.16	0.15	0.89	0.030	0.08	16.4	5.3	0.17	132	50.90	0.02	0.36
CC29960		44.5	1.04	4.80	0.11	0.04	0.12	0.031	0.07	8.7	2.1	0.05	19	14.65	0.02	0.27
CC29961		45.1	1.69	4.26	0.13	0.09	0.29	0.036	0.11	8.4	3.7	0.10	30	35.60	0.02	0.34

Comments: Interference: Ca>10% on ICP-MS As,ICP-AES results shown. Gold determinations by ME-MS41 are semi-quantitative due to the small sample weight used (0.5g).

ALS Chemex

EXCELLENCE IN ANALYTICAL CHEMISTRY

ALS Canada Ltd.

212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: STRATEGIC METALS LTD.
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO

Finalized Date: 9-JUL-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07067610

Sample Description	Method	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41
	Analyte	Ni	P	Pb	Rb	Re	S	Sb	Sc	Se	Sn	Sr	Ta	Te	Th	Ti
	Units	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%
	LOR	0.2	10	0.2	0.1	0.001	0.01	0.05	0.1	0.2	0.2	0.2	0.01	0.01	0.2	0.005
CC29886		109.0	660	16.4	10.4	0.011	0.06	4.02	4.2	7.9	0.7	29.9	<0.01	0.12	2.3	0.006
CC29887		13.4	320	12.7	12.0	0.001	0.02	1.36	2.9	3.3	0.5	14.1	<0.01	0.08	3.0	0.011
CC29901		38.9	1010	11.6	7.2	0.008	0.23	4.02	2.7	15.9	0.5	105.5	<0.01	0.13	0.4	0.007
CC29902		17.9	150	12.6	9.3	<0.001	0.04	3.42	1.6	2.8	0.9	22.9	<0.01	0.12	2.0	0.016
CC29903		4.2	120	7.6	4.8	0.016	0.12	1.66	0.7	3.3	0.3	23.8	<0.01	0.10	0.9	<0.005
CC29904		22.8	490	17.9	14.5	0.001	0.14	14.85	2.7	11.6	0.9	81.8	<0.01	0.23	2.6	0.016
CC29905		17.1	480	16.3	9.2	0.001	0.14	12.15	1.7	12.5	0.7	66.0	<0.01	0.24	1.4	0.016
CC29906		35.5	790	14.4	14.0	0.003	0.31	14.40	3.4	11.3	0.8	69.2	<0.01	0.23	1.6	0.012
CC29907		79.4	380	13.1	18.4	<0.001	0.06	10.85	2.9	4.5	0.9	31.2	<0.01	0.16	3.0	0.013
CC29908		75.6	350	10.1	10.0	0.006	0.04	3.50	4.0	3.3	0.5	40.0	<0.01	0.08	2.7	0.006
CC29909		91.2	150	7.6	6.5	0.010	0.03	4.18	2.3	2.8	0.4	16.3	<0.01	0.09	1.3	<0.005
CC29910		332.0	360	7.9	6.0	0.017	0.03	8.35	3.2	10.9	0.5	16.3	<0.01	0.17	1.4	<0.005
CC29911		1190.0	2640	17.8	13.0	0.036	0.05	83.40	4.4	45.9	0.8	72.9	0.01	0.57	1.1	0.007
CC29912		310.0	710	14.5	13.6	0.005	0.07	36.00	5.6	17.3	0.8	219.0	<0.01	0.21	3.1	0.009
CC29913		348.0	880	11.1	12.4	0.003	0.08	21.10	7.0	8.4	0.8	118.5	0.01	0.16	2.8	0.012
CC29914		193.5	630	11.1	7.6	0.001	0.11	10.30	3.9	6.3	0.7	146.5	0.01	0.13	1.5	0.008
CC29915		100.5	360	16.1	14.6	0.002	0.03	19.05	3.7	11.8	0.8	16.4	<0.01	0.14	2.7	0.017
CC29916		194.5	410	14.0	14.4	0.001	0.04	9.31	3.1	10.3	0.8	7.5	<0.01	0.15	2.1	0.016
CC29917		123.0	310	13.5	12.5	0.002	0.03	5.72	2.7	4.8	0.7	8.1	<0.01	0.11	2.1	0.017
CC29918		61.0	230	9.5	9.5	<0.001	0.02	3.44	1.6	2.8	0.7	7.2	<0.01	0.08	1.5	0.013
CC29919		66.8	300	13.2	12.3	0.009	0.36	2.99	3.0	3.9	0.4	98.0	<0.01	0.08	3.4	<0.005
CC29920		91.5	500	10.4	10.1	0.011	0.06	2.00	3.9	6.1	0.4	42.1	<0.01	0.07	2.1	<0.005
CC29921		18.9	300	9.0	9.2	0.004	0.10	5.38	1.9	5.4	0.4	24.3	<0.01	0.10	1.8	0.013
CC29922		9.4	350	12.3	9.8	0.004	0.25	7.45	1.8	6.3	0.5	87.5	<0.01	0.17	2.1	0.009
CC29923		6.5	360	12.0	9.7	0.002	0.30	5.26	1.0	5.4	0.5	67.1	<0.01	0.15	1.0	0.006
CC29924		6.6	310	8.9	6.2	0.003	0.18	1.35	1.3	3.8	0.5	20.5	<0.01	0.11	0.5	0.009
CC29925		6.4	70	7.9	4.3	0.009	0.06	0.61	2.1	1.6	0.4	16.2	<0.01	0.08	1.7	0.005
CC29926		4.0	130	7.4	4.6	0.004	0.03	0.44	1.0	1.4	0.3	10.4	<0.01	0.09	0.6	<0.005
CC29927		36.7	860	12.0	12.3	0.003	0.05	2.27	4.3	3.8	0.6	52.9	<0.01	0.09	3.0	0.008
CC29951		36.8	590	11.7	12.0	0.002	0.05	1.90	4.7	2.1	0.5	48.2	<0.01	0.07	4.2	0.015
CC29952		37.1	610	11.4	12.2	0.001	0.05	1.84	4.5	1.8	0.6	62.5	<0.01	0.06	3.7	0.012
CC29953		33.7	330	12.1	9.8	0.005	0.02	2.19	3.9	3.0	0.5	25.5	<0.01	0.06	4.1	0.008
CC29954		22.1	600	7.2	11.4	0.002	0.11	1.23	2.7	2.9	0.5	56.6	<0.01	0.05	1.9	0.006
CC29955		36.5	950	9.5	6.9	0.005	0.10	2.34	2.7	5.0	0.5	63.3	<0.01	0.07	1.1	0.006
CC29956		143.5	690	8.0	6.1	0.006	0.15	12.65	3.2	7.6	0.3	189.5	0.01	0.07	0.7	0.009
CC29957		352.0	870	13.5	10.0	0.006	0.11	23.00	4.2	11.9	0.6	90.6	0.01	0.19	1.6	0.010
CC29958		209.0	830	13.3	11.2	0.003	0.10	16.30	5.4	8.0	0.7	114.5	0.01	0.14	1.9	0.010
CC29959		195.5	730	14.6	11.9	0.006	0.10	28.00	4.9	14.2	0.6	157.5	0.01	0.19	1.2	0.009
CC29960		41.2	1120	10.4	8.3	0.007	0.10	3.71	2.9	14.3	0.8	89.8	<0.01	0.16	1.1	0.005
CC29961		85.7	1140	14.3	15.3	0.017	0.17	10.65	3.4	20.4	0.8	177.0	<0.01	0.21	1.4	<0.005

Comments: Interference: Ca>10% on ICP-MS As,ICP-AES results shown. Gold determinations by ME-MS41 are semi-quantitative due to the small sample weight used (0.5g).

ALS Chemex
EXCELLENCE IN ANALYTICAL CHEMISTRY
ALS Canada Ltd.
212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: STRATEGIC METALS LTD.
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO

CERTIFICATE OF ANALYSIS VA07067610

Sample Description	Method / Analyte / Units / LOR	ME-MS41 Tl ppm 0.02	ME-MS41 U ppm 0.05	ME-MS41 V ppm 1	ME-MS41 W ppm 0.05	ME-MS41 Y ppm 0.05	ME-MS41 Zn ppm 2	ME-MS41 Zr ppm 0.5
CC29886		1.12	7.83	293	0.28	24.00	266	1.4
CC29887		0.56	1.26	86	0.16	4.19	54	1.2
CC29901		1.23	6.41	104	0.12	9.83	116	1.1
CC29902		1.05	0.81	228	0.18	2.28	72	1.3
CC29903		1.12	5.34	56	0.12	1.88	7	<0.5
CC29904		2.34	1.97	427	0.26	4.24	88	1.3
CC29905		1.57	1.79	278	0.24	3.18	68	<0.5
CC29906		2.64	3.84	259	0.30	9.89	136	0.6
CC29907		1.42	1.91	476	0.23	5.03	288	2.1
CC29908		0.71	3.42	233	0.17	17.10	210	1.5
CC29909		0.80	1.74	181	0.14	11.50	219	0.6
CC29910		1.83	4.05	309	0.27	29.80	642	1.5
CC29911		12.25	13.85	1375	0.62	65.50	2930	1.8
CC29912		2.06	9.00	1275	0.30	36.60	2470	3.7
CC29913		2.28	7.34	835	0.28	39.80	2380	5.6
CC29914		1.43	9.17	536	0.32	36.70	579	3.3
CC29915		2.38	1.83	794	0.23	8.68	1110	1.4
CC29916		2.49	1.87	330	0.24	5.73	585	1.0
CC29917		1.72	1.17	264	0.21	4.65	459	0.8
CC29918		0.82	0.75	209	0.17	2.86	197	<0.5
CC29919		1.71	1.59	91	0.09	9.74	157	4.7
CC29920		0.80	2.67	135	0.12	19.00	121	1.4
CC29921		0.89	2.24	164	0.15	4.92	61	0.7
CC29922		1.80	3.62	187	0.19	3.78	35	0.9
CC29923		2.58	1.40	277	0.22	2.36	34	<0.5
CC29924		1.22	2.32	80	0.16	3.16	15	<0.5
CC29925		0.35	4.53	34	0.11	5.75	26	1.5
CC29926		0.30	3.36	32	0.10	2.61	13	<0.5
CC29927		0.70	3.08	178	0.11	18.10	169	2.2
CC29951		0.42	1.82	105	0.12	12.00	126	2.8
CC29952		0.28	2.90	115	0.12	13.10	140	3.0
CC29953		0.42	2.63	121	0.12	9.15	133	2.3
CC29954		0.15	1.36	57	0.08	7.62	79	1.3
CC29955		0.41	5.14	229	0.13	10.60	186	0.9
CC29956		1.26	7.33	405	0.17	30.50	1275	3.1
CC29957		2.48	7.33	798	0.34	37.20	1215	4.3
CC29958		1.38	4.31	739	0.32	44.00	1170	4.0
CC29959		2.74	13.80	1050	0.30	47.10	2480	3.8
CC29960		1.38	15.60	185	0.15	14.55	104	0.6
CC29961		2.46	8.77	324	0.23	13.90	220	2.0

Comments: Interference: Ca>10% on ICP-MS As,ICP-AES results shown. Gold determinations by ME-MS41 are semi-quantitative due to the small sample weight used (0.5g).

ALS Chemex

EXCELLENCE IN ANALYTICAL CHEMISTRY

ALS Canada Ltd.

212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: STRATEGIC METALS LTD.
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO

Finalized Date: 9-JUL-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07067610

Sample Description	Method	WEI-21	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41
	Analyte	Recvd Wt.	Ag	Al	As	Au	B	Ba	Be	Bi	Ca	Cd	Ce	Co	Cr	Cs
	Units	kg	ppm	%	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppm	ppm	ppm
	LOR	0.02	0.01	0.01	0.1	0.2	10	10	0.05	0.01	0.01	0.01	0.02	0.1	1	0.05
CC29962		0.20	0.25	0.38	15.4	<0.2	<10	180	0.21	0.14	0.02	0.32	9.29	1.4	11	0.35
CC29963		0.12	0.17	1.14	33.6	<0.2	<10	300	0.28	0.29	0.03	0.38	19.95	4.0	25	1.11
CC29964		0.16	0.34	1.66	22.7	<0.2	<10	290	0.49	0.25	0.04	0.34	20.30	5.1	29	1.24
CC29965		0.14	0.31	0.78	16.9	<0.2	<10	130	0.18	0.21	0.02	0.13	19.65	2.3	14	0.84
CC29966		0.18	0.94	0.67	24.9	<0.2	<10	320	0.32	0.15	0.01	0.74	11.00	1.9	17	0.51
CC29967		0.14	1.20	0.49	33.1	<0.2	<10	5260	0.88	0.12	2.38	12.55	40.60	3.5	31	0.51
CC29968		0.08	2.24	0.59	14.1	<0.2	<10	2320	0.87	0.11	2.48	11.20	39.30	6.3	22	0.54
CC29969		0.14	1.19	0.61	46.7	<0.2	<10	1310	1.17	0.21	2.09	13.25	55.20	6.3	44	0.56
CC29970		0.10	0.47	0.75	5.2	<0.2	<10	3750	0.43	0.14	0.16	1.49	17.90	2.1	17	0.61
CC29971		0.12	1.06	1.45	18.9	<0.2	<10	1430	0.85	0.22	0.46	13.40	29.70	7.4	48	0.95
CC29972		0.14	1.42	1.44	17.2	<0.2	<10	2230	0.72	0.23	0.37	16.85	33.60	9.7	43	0.83
CC29973		0.18	1.11	1.56	8.6	<0.2	<10	2530	0.65	0.22	0.44	12.05	32.40	9.4	42	0.84
CC29974		0.20	0.32	1.27	8.5	<0.2	<10	1490	0.49	0.19	0.33	2.22	28.20	7.2	32	0.77
CC29975		0.18	0.37	1.66	8.7	<0.2	<10	1720	0.62	0.21	0.36	1.29	27.60	7.0	28	1.10
CC29976		0.14	1.35	0.31	17.6	<0.2	<10	340	0.15	0.23	0.01	0.54	8.82	0.6	14	0.61
CC29977		0.14	0.78	0.96	26.3	<0.2	<10	170	0.19	0.23	0.03	0.33	18.60	3.1	22	1.05
CC29978		0.12	0.40	0.73	12.5	<0.2	<10	990	0.50	0.15	0.37	4.43	13.55	3.1	24	0.62
CC29979		0.16	0.41	0.71	18.5	<0.2	<10	820	0.80	0.16	0.33	4.72	14.90	5.2	17	0.60
CC29980		0.16	0.08	0.40	27.6	<0.2	<10	220	0.43	0.16	0.10	1.82	7.60	5.6	17	0.50
CC29981		0.08	1.00	0.45	16.6	<0.2	<10	420	0.26	0.10	0.66	4.86	6.48	2.7	19	1.10
CC29982		0.20	3.48	0.69	93.2	<0.2	10	620	0.78	0.27	3.69	43.50	18.75	11.7	52	1.37
CC29983		0.14	3.99	0.78	69.2	<0.2	10	1450	1.20	0.24	1.84	29.90	24.80	5.9	100	0.93
CC29984		0.08	1.46	0.57	36.4	<0.2	10	2080	0.98	0.15	2.47	16.20	33.70	5.4	55	0.58
CC29985		0.08	0.81	0.46	30.8	<0.2	<10	1690	0.79	0.13	2.29	7.27	24.00	1.9	38	0.52
CC29986		0.06	0.61	0.62	2.3	<0.2	<10	1800	0.24	0.18	0.44	0.58	14.45	3.2	10	0.77
CC29987		0.08	1.72	0.94	2.0	<0.2	<10	2850	0.37	0.12	0.39	0.46	18.20	3.5	10	0.71
CC29988		0.16	1.59	1.44	5.7	<0.2	<10	6220	0.67	0.21	0.13	0.98	22.40	8.9	23	0.97
CC29989		0.18	0.86	0.78	9.8	<0.2	<10	570	0.31	0.26	0.02	0.25	11.05	8.0	16	0.94
CC29990		0.22	1.77	0.76	11.6	<0.2	10	4030	0.85	0.26	0.55	1.41	19.45	8.9	15	0.89
CC29991		0.04	0.63	0.68	3.8	<0.2	10	3940	0.29	0.10	2.30	0.71	6.78	2.3	12	0.54
CC29992		0.12	0.65	0.81	9.0	<0.2	<10	2250	0.49	0.31	0.01	0.45	14.25	23.7	19	0.75
CC29993		0.22	0.84	0.76	31.9	<0.2	10	3500	0.93	0.17	0.21	14.65	23.90	6.6	37	0.91
CC29994		0.18	0.26	1.12	25.8	<0.2	<10	3230	1.14	0.21	0.32	6.70	16.45	10.4	33	0.74
CC29995		0.16	1.11	1.17	35.3	<0.2	<10	5730	1.01	0.20	0.26	10.25	32.80	6.2	48	0.75
CC29996		0.14	1.63	2.50	45.0	<0.2	<10	2070	1.92	0.27	0.84	14.30	74.60	11.5	75	1.44
CC29997		0.16	3.26	0.80	62.2	<0.2	10	1450	1.40	0.22	1.61	29.40	26.30	5.5	103	0.73
CC29998		0.14	0.16	1.45	40.5	<0.2	<10	270	0.36	0.28	0.06	0.56	19.35	6.0	37	1.29
CC29999		0.20	0.95	1.25	47.8	<0.2	<10	3270	1.02	0.23	0.46	7.66	27.90	9.8	37	0.98
CC30000		0.20	0.25	1.00	38.6	<0.2	<10	680	0.48	0.24	0.03	0.96	14.90	6.7	33	0.81
CC39551		0.24	0.17	1.41	13.2	<0.2	<10	460	0.44	0.23	0.08	0.31	13.70	8.8	27	0.98

Comments: Interference: Ca>10% on ICP-MS As,ICP-AES results shown. Gold determinations by ME-MS41 are semi-quantitative due to the small sample weight used (0.5g).

ALS Chemex

EXCELLENCE IN ANALYTICAL CHEMISTRY

ALS Canada Ltd.

212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: STRATEGIC METALS LTD.
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO

Finalized Date: 9-JUL-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07067610

Sample Description	Method	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41
	Analyte	Cu	Fe	Ga	Ge	Hf	Hg	In	K	La	Li	Mg	Mn	Mo	Na	Nb
	Units	ppm	%	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	%	ppm	ppm	%	ppm
	LOR	0.2	0.01	0.05	0.05	0.02	0.01	0.005	0.01	0.2	0.1	0.01	5	0.05	0.01	0.05
CC29962		33.3	1.18	2.39	<0.05	0.02	0.04	0.020	0.06	5.0	2.0	0.05	35	15.50	0.01	0.24
CC29963		24.3	3.39	8.28	0.08	0.02	0.03	0.036	0.09	10.6	4.9	0.12	122	24.10	0.01	1.07
CC29964		43.8	3.18	6.47	0.09	0.09	0.10	0.041	0.10	10.7	13.5	0.20	155	28.20	0.01	0.87
CC29965		14.7	1.77	5.93	0.06	0.03	0.02	0.014	0.04	10.4	1.6	0.04	43	14.50	0.01	0.71
CC29966		29.3	1.63	2.79	0.07	0.06	0.06	0.025	0.09	6.5	3.7	0.07	44	19.40	0.01	0.33
CC29967		72.3	1.00	2.30	0.14	0.12	0.53	0.018	0.03	28.6	2.0	0.10	60	38.80	0.05	0.25
CC29968		47.1	1.00	1.85	0.13	0.11	0.72	0.022	0.03	26.7	1.6	0.15	114	13.10	0.04	0.24
CC29969		73.9	1.93	3.06	0.15	0.14	0.62	0.034	0.05	31.8	3.7	0.33	128	83.00	0.02	0.30
CC29970		30.0	0.93	2.61	0.06	0.05	0.17	0.020	0.06	9.4	5.2	0.10	31	5.68	0.03	0.20
CC29971		52.2	1.69	4.85	0.11	0.09	0.22	0.033	0.09	15.8	11.7	0.29	117	3.67	0.02	0.50
CC29972		70.7	2.23	5.17	0.14	0.18	0.24	0.036	0.10	18.3	13.1	0.34	131	5.18	0.03	0.67
CC29973		67.9	1.74	5.15	0.11	0.16	0.24	0.039	0.11	17.4	14.9	0.38	172	5.29	0.03	0.64
CC29974		28.2	1.86	4.21	0.08	0.07	0.07	0.025	0.08	14.7	12.3	0.30	127	7.51	0.02	0.52
CC29975		27.2	2.03	5.32	0.09	0.06	0.09	0.032	0.10	14.4	12.6	0.28	142	6.59	0.02	0.50
CC29976		15.6	1.56	3.02	0.08	<0.02	0.03	0.026	0.20	6.1	1.2	0.02	10	39.60	0.01	0.17
CC29977		17.0	2.52	6.26	0.08	0.03	0.06	0.023	0.08	10.4	5.1	0.10	66	21.50	0.01	0.84
CC29978		30.5	1.15	2.92	0.06	0.04	0.15	0.019	0.07	7.9	3.9	0.09	82	14.85	0.02	0.27
CC29979		46.8	1.63	2.35	0.07	0.05	0.17	0.025	0.06	8.9	3.2	0.08	55	28.20	0.01	0.20
CC29980		31.8	1.71	1.68	0.06	0.02	0.03	0.025	0.06	5.5	1.6	0.03	21	37.50	0.01	0.15
CC29981		25.5	0.79	1.94	0.06	0.05	0.22	0.012	0.05	3.5	0.8	0.09	12	28.80	0.02	0.14
CC29982		133.0	2.07	4.07	0.19	0.14	1.14	0.040	0.17	11.6	2.6	1.24	132	87.90	0.02	0.20
CC29983		152.0	1.86	4.16	0.18	0.15	1.28	0.035	0.11	16.0	4.2	0.24	114	59.30	0.02	0.22
CC29984		70.3	1.24	2.86	0.14	0.16	0.65	0.024	0.05	20.2	3.3	0.21	129	44.20	0.03	0.22
CC29985		61.5	1.00	2.53	0.10	0.12	0.34	0.021	0.05	14.7	2.9	0.15	59	22.80	0.02	0.23
CC29986		14.4	1.25	2.13	0.06	0.05	0.19	0.016	0.06	7.1	2.1	0.11	53	2.15	0.03	0.17
CC29987		20.8	1.47	1.87	0.07	0.05	0.21	0.020	0.04	8.7	1.3	0.07	23	1.63	0.03	0.19
CC29988		43.5	2.24	4.46	0.08	0.09	0.31	0.035	0.08	11.9	8.8	0.17	130	4.65	0.05	0.31
CC29989		75.2	2.23	4.89	<0.05	0.04	0.04	0.032	0.08	6.1	1.7	0.05	44	6.37	0.02	0.22
CC29990		78.8	2.68	2.15	0.07	0.06	0.17	0.043	0.16	11.1	2.3	0.09	135	4.49	0.04	0.07
CC29991		17.1	0.93	2.11	<0.05	0.13	0.11	0.018	0.05	3.4	2.3	0.39	52	3.23	0.05	0.17
CC29992		62.0	4.58	2.57	0.06	0.18	0.10	0.041	0.10	6.5	2.0	0.05	162	3.11	0.03	0.16
CC29993		91.6	2.02	3.50	0.10	0.06	0.21	0.032	0.12	13.9	3.9	0.06	80	39.40	0.04	0.13
CC29994		52.8	2.39	4.82	0.06	0.11	0.35	0.038	0.07	8.6	7.1	0.14	65	85.80	0.03	0.28
CC29995		73.3	1.55	4.36	0.09	0.05	0.33	0.024	0.05	14.6	6.2	0.07	81	50.80	<0.01	0.37
CC29996		57.0	2.98	6.28	0.12	0.15	0.39	0.049	0.08	29.9	16.0	0.26	315	58.00	0.03	0.84
CC29997		167.0	1.79	4.35	0.12	0.15	0.94	0.040	0.11	16.0	5.4	0.25	72	43.70	0.02	0.26
CC29998		23.8	3.63	7.65	0.06	0.05	0.03	0.033	0.08	10.1	11.6	0.21	104	30.90	0.01	1.30
CC29999		65.9	2.71	4.56	0.09	0.07	0.35	0.039	0.10	17.3	7.6	0.18	153	43.90	0.03	0.38
CC30000		44.0	2.87	4.68	0.06	0.04	0.07	0.036	0.10	8.7	4.7	0.10	67	39.20	0.02	0.54
CC39551		29.8	3.04	4.98	0.06	0.06	0.09	0.036	0.09	6.3	19.5	0.33	96	5.61	0.02	0.29

Comments: Interference: Ca>10% on ICP-MS As,ICP-AES results shown. Gold determinations by ME-MS41 are semi-quantitative due to the small sample weight used (0.5g).

ALS Chemex

EXCELLENCE IN ANALYTICAL CHEMISTRY

ALS Canada Ltd.

212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: STRATEGIC METALS LTD.
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO

Finalized Date: 9-JUL-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07067610

Sample Description	Method	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41
	Analyte	Ni	P	Pb	Rb	Re	S	Sb	Sc	Se	Sn	Sr	Ta	Te	Th	Ti
	Units	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%
	LOR	0.2	10	0.2	0.1	0.001	0.01	0.05	0.1	0.2	0.2	0.2	0.01	0.01	0.2	0.005
CC29962		13.9	250	7.6	6.8	0.001	0.14	1.86	1.6	2.3	0.4	35.5	<0.01	0.08	1.5	0.007
CC29963		30.0	410	17.5	14.3	<0.001	0.10	4.26	2.7	3.0	0.9	40.2	<0.01	0.14	2.5	0.025
CC29964		25.6	440	15.4	16.3	<0.001	0.14	5.05	3.3	4.6	0.8	33.3	<0.01	0.13	3.7	0.017
CC29965		18.9	150	11.1	7.6	<0.001	0.02	3.73	1.5	1.7	0.8	7.8	<0.01	0.10	2.3	0.023
CC29966		27.9	300	9.9	10.4	0.003	0.16	8.61	2.1	5.9	0.4	63.8	<0.01	0.13	2.3	0.007
CC29967		389.0	640	9.5	5.9	0.001	0.10	11.70	2.6	5.7	0.4	216.0	0.01	0.11	0.5	0.007
CC29968		116.0	1340	9.9	4.1	0.003	0.21	4.86	2.8	6.2	0.3	206.0	0.01	0.07	0.4	0.008
CC29969		328.0	530	14.0	6.8	0.001	0.09	11.25	5.2	8.0	1.0	129.0	0.01	0.14	2.0	0.005
CC29970		16.8	550	8.9	8.6	0.004	0.08	1.36	2.6	2.3	0.4	67.5	<0.01	0.04	2.1	0.005
CC29971		138.5	540	13.5	13.5	0.008	0.04	8.55	5.3	7.6	0.5	44.7	<0.01	0.09	4.3	0.011
CC29972		113.5	540	13.5	14.2	0.008	0.07	10.40	6.1	8.4	0.6	54.1	<0.01	0.09	5.1	0.015
CC29973		181.5	600	10.1	13.3	0.004	0.06	5.99	6.3	3.3	0.7	66.0	<0.01	0.07	4.8	0.017
CC29974		65.2	460	9.8	11.5	0.003	0.03	2.45	4.1	1.8	0.5	37.1	<0.01	0.05	4.1	0.016
CC29975		53.5	620	10.5	16.0	0.005	0.04	1.76	4.7	2.3	0.6	36.7	<0.01	0.05	2.8	0.010
CC29976		9.3	390	17.2	11.7	0.001	0.44	7.76	1.1	11.7	0.7	63.1	<0.01	0.19	1.3	0.006
CC29977		28.5	450	10.8	12.5	<0.001	0.08	6.20	2.1	4.5	0.7	24.8	<0.01	0.13	2.6	0.023
CC29978		42.5	600	8.4	9.4	0.012	0.07	2.29	2.3	4.0	0.5	31.0	<0.01	0.09	1.2	0.005
CC29979		107.0	340	9.8	9.2	0.010	0.03	3.61	3.5	4.2	0.4	28.5	<0.01	0.09	1.8	<0.005
CC29980		292.0	200	9.5	7.5	0.006	0.02	5.37	1.9	3.3	0.4	9.1	<0.01	0.10	1.0	<0.005
CC29981		79.7	800	6.7	7.7	0.003	0.15	8.97	2.0	5.4	0.4	30.2	<0.01	0.08	0.8	0.005
CC29982		409.0	910	18.5	15.4	0.021	0.05	34.60	6.4	15.2	0.9	104.5	0.01	0.23	3.2	0.006
CC29983		310.0	1250	15.8	13.3	0.009	0.10	24.40	5.7	12.0	0.8	100.5	0.01	0.24	1.7	0.006
CC29984		209.0	910	10.9	6.6	0.013	0.18	13.05	3.5	13.1	0.6	151.5	0.01	0.12	1.1	0.005
CC29985		100.5	870	8.4	7.1	0.008	0.14	9.45	2.2	7.3	0.5	133.5	<0.01	0.11	0.9	0.005
CC29986		13.9	1000	7.8	6.9	<0.001	0.15	0.58	2.5	1.5	0.3	51.7	<0.01	0.03	0.9	<0.005
CC29987		19.1	950	9.7	3.6	<0.001	0.16	0.39	3.2	1.9	0.2	56.8	<0.01	0.04	0.8	0.007
CC29988		38.5	830	12.8	9.5	0.001	0.06	1.10	3.4	2.5	0.5	35.0	<0.01	0.06	1.5	0.005
CC29989		49.6	400	13.4	12.6	0.001	0.05	2.04	2.8	3.4	0.6	21.5	<0.01	0.09	1.7	0.005
CC29990		61.2	1720	15.8	11.2	0.001	0.04	1.95	5.7	4.2	0.4	153.5	<0.01	0.14	2.6	<0.005
CC29991		15.9	1110	5.4	6.4	0.006	0.16	1.28	2.2	2.7	0.3	215.0	<0.01	0.04	0.7	<0.005
CC29992		86.3	270	18.1	12.5	0.001	0.12	2.57	7.4	4.0	0.6	25.0	<0.01	0.08	4.6	<0.005
CC29993		96.9	1070	12.5	13.1	0.002	0.07	18.85	3.2	6.8	0.8	103.0	0.01	0.14	1.0	0.006
CC29994		190.5	380	12.6	10.2	<0.001	0.05	7.34	4.5	3.1	1.0	34.0	<0.01	0.12	2.0	0.006
CC29995		206.0	540	13.2	7.7	<0.001	0.07	11.45	2.4	4.1	0.8	49.0	<0.01	0.14	0.7	0.009
CC29996		212.0	490	20.1	14.8	0.001	0.06	9.78	6.1	6.5	0.9	71.3	0.01	0.12	3.3	0.011
CC29997		278.0	1670	11.2	12.2	0.003	0.06	23.00	6.5	8.0	0.9	90.9	0.01	0.24	3.0	0.007
CC29998		104.0	270	14.1	13.8	0.001	0.02	5.68	3.1	4.0	0.8	11.6	<0.01	0.10	3.0	0.030
CC29999		250.0	720	13.2	12.4	0.002	0.06	7.87	5.0	6.2	0.7	54.6	<0.01	0.14	1.5	0.009
CC30000		148.0	350	14.8	13.5	0.002	0.04	7.46	3.2	5.4	0.7	13.1	<0.01	0.12	2.2	0.010
CC39551		37.3	430	13.8	12.0	0.017	0.08	1.31	4.9	4.4	0.6	22.6	<0.01	0.05	3.1	<0.005

Comments: Interference: Ca>10% on ICP-MS As,ICP-AES results shown. Gold determinations by ME-MS41 are semi-quantitative due to the small sample weight used (0.5g).

ALS Chemex

EXCELLENCE IN ANALYTICAL CHEMISTRY

ALS Canada Ltd.

212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: STRATEGIC METALS LTD.
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO

Finalized Date: 9-JUL-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07067610

Sample Description	Method	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41
	Analyte	Tl	U	V	W	Y	Zn	Zr
	Units	ppm	ppm	ppm	ppm	ppm	ppm	ppm
	LOR	0.02	0.05	1	0.05	0.05	2	0.5
CC29962		1.07	2.83	76	0.15	3.02	38	0.6
CC29963		1.13	1.09	245	0.26	3.12	100	0.8
CC29964		1.62	1.41	209	0.22	3.51	82	3.2
CC29965		0.56	0.59	212	0.18	1.89	61	1.0
CC29966		1.98	1.91	162	0.16	5.34	68	2.2
CC29967		1.30	26.60	436	0.30	44.90	658	3.5
CC29968		1.45	19.95	254	0.14	36.10	325	2.9
CC29969		2.41	8.29	537	0.46	40.20	867	3.8
CC29970		0.31	3.20	122	0.08	9.22	65	0.8
CC29971		1.04	6.52	646	0.14	18.80	1500	3.1
CC29972		1.22	4.59	408	0.13	21.80	1160	6.4
CC29973		1.65	3.93	227	0.13	20.60	1025	5.6
CC29974		0.50	1.31	124	0.14	10.65	249	2.1
CC29975		0.54	1.81	133	0.14	11.95	191	1.4
CC29976		3.60	1.43	149	0.23	2.58	37	<0.5
CC29977		1.22	1.09	272	0.19	2.98	98	1.3
CC29978		0.89	2.90	242	0.27	10.15	147	0.8
CC29979		0.95	4.27	241	0.18	18.00	291	1.1
CC29980		0.81	2.50	269	0.18	6.60	507	0.5
CC29981		1.17	1.94	322	0.11	7.18	340	1.6
CC29982		1.88	7.98	1195	0.25	39.40	3310	5.3
CC29983		1.56	8.52	1095	0.33	47.00	2350	4.2
CC29984		1.50	11.00	580	0.27	36.10	1145	5.2
CC29985		1.16	9.92	614	0.25	21.60	394	3.8
CC29986		0.12	1.15	21	0.05	5.48	38	1.1
CC29987		0.07	1.83	13	0.05	13.15	21	1.2
CC29988		0.19	2.25	64	0.08	13.00	118	1.2
CC29989		0.27	1.05	93	0.08	3.62	236	1.4
CC29990		0.10	2.18	55	0.05	19.50	256	1.1
CC29991		0.10	1.42	46	<0.05	4.40	67	3.2
CC29992		0.21	0.99	69	<0.05	9.39	213	7.4
CC29993		0.32	5.69	590	0.15	31.00	636	0.8
CC29994		1.34	4.84	500	0.28	24.00	601	2.5
CC29995		1.95	10.00	570	0.22	21.50	429	1.0
CC29996		2.51	12.45	802	0.35	41.30	883	5.1
CC29997		1.39	7.56	824	0.33	41.60	1535	5.5
CC29998		1.39	1.24	571	0.22	3.28	343	2.2
CC29999		2.41	3.92	517	0.22	25.80	901	1.3
CC30000		1.43	2.02	488	0.21	5.91	526	1.3
CC39551		0.45	0.91	62	<0.05	6.13	96	1.9

Comments: Interference: Ca>10% on ICP-MS As,ICP-AES results shown. Gold determinations by ME-MS41 are semi-quantitative due to the small sample weight used (0.5g).

ALS Chemex
EXCELLENCE IN ANALYTICAL CHEMISTRY
ALS Canada Ltd.
212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

STRATEGIC METALS LTD.
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Finalized Date: 20-JUL-2007
Account: MTT

CERTIFICATE VA07067539

Project: NIMO

P.O. No.:

This report is for 6 Rock samples submitted to our lab in Vancouver, BC, Canada on 28-JUN-2007.

The following have access to data associated with this certificate:

JOAN MARIACHER

SAMPLE PREPARATION

ALS CODE	DESCRIPTION
WEI-21	Received Sample Weight
LOG-22	Sample login - Rcd w/o BarCode
CRU-31	Fine crushing - 70% <2mm
SPL-21	Split sample - riffle splitter
PUL-31	Pulverize split to 85% <75 um

ANALYTICAL PROCEDURES

ALS CODE	DESCRIPTION	
ME-MS61	48 element four acid ICP-MS	
Hg-CV41	Trace Hg - cold vapor/AAS	FIMS
Ni-AA62	Ore grade Ni - four acid / AA	AAS
PGM-ICP23	Pt, Pd, Au 30g FA ICP	ICP-AES

To: **STRATEGIC METALS LTD.**
ATTN: JOAN MARIACHER
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

This is the Final Report and supersedes any preliminary report with this certificate number. Results apply to samples as submitted. All pages of this report have been checked and approved for release.

Signature: Lawrence Ng

Lawrence Ng, Laboratory Manager - Vancouver

ALS Chemex
EXCELLENCE IN ANALYTICAL CHEMISTRY
ALS Canada Ltd.
212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

STRATEGIC METALS LTD.
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO

Finalized Date: 20-JUL-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07067539

Sample Description	Method / Analyte / Units / LOR	WEI-21 Recvd Wt. kg 0.02	PGM-ICP23 Au ppm 0.001	PGM-ICP23 Pt ppm 0.005	PGM-ICP23 Pd ppm 0.001	ME-MS61 Ag ppm 0.01	ME-MS61 Al % 0.01	ME-MS61 As ppm 0.2	ME-MS61 Ba ppm 10	ME-MS61 Be ppm 0.05	ME-MS61 Bi ppm 0.01	ME-MS61 Ca % 0.01	ME-MS61 Cd ppm 0.02	ME-MS61 Ce ppm 0.01	ME-MS61 Co ppm 0.1	ME-MS61 Cr ppm 1
C385634		0.60	<0.001	<0.005	0.001	0.40	6.36	31.3	610	2.05	0.17	1.06	0.25	41.30	2.1	74
C385635		1.00	<0.001	<0.005	0.002	0.25	5.20	22.9	1920	2.36	0.14	5.76	6.47	44.40	27.5	67
C385636		0.38	0.241	0.470	0.282	3.23	0.71	3820.0	690	0.17	1.08	0.03	0.55	2.08	58.0	38
C385637		0.96	0.005	0.005	0.006	0.36	7.31	157.0	720	3.02	0.28	0.05	0.07	65.00	1.5	92
C385638		0.30	0.025	<0.005	0.041	6.37	2.73	138.0	190	9.72	3.30	1.21	3.19	55.20	0.5	21
C385639		0.42	<0.001	<0.005	0.007	0.90	4.01	58.7	440	2.80	0.31	1.04	5.39	49.20	4.4	93

Comments: Interference: Mo>400ppm on ICP-MS Cd,ICP-AES results shown. REE's may not be totally soluble in MS61 method.

ALS Chemex
EXCELLENCE IN ANALYTICAL CHEMISTRY
ALS Canada Ltd.
212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: STRATEGIC METALS LTD.
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO

Finalized Date: 20-JUL-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07067539

Sample Description	Method	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	Hg-CV41	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61
	Analyte	Cs	Cu	Fe	Ga	Ge	Hf	Hg	In	K	La	Li	Mg	Mn	Mo	Na
	Units	ppm	ppm	%	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	%	ppm	ppm	%
	LOR	0.05	0.2	0.01	0.05	0.05	0.1	0.01	0.005	0.01	0.5	0.2	0.01	5	0.05	0.01
C385634		9.53	19.9	2.06	17.80	0.14	2.8	0.42	0.044	2.41	23.8	13.1	0.45	20	41.60	0.13
C385635		6.26	119.5	5.17	13.60	0.19	2.3	0.34	0.078	1.85	24.8	9.1	0.38	366	22.30	0.09
C385636		0.94	133.0	19.15	3.82	17.50	0.3	0.29	0.050	0.20	0.9	4.3	0.04	125	2690.00	0.02
C385637		10.45	7.2	0.99	24.80	0.50	3.8	0.14	0.033	2.41	36.2	14.8	0.57	18	116.00	0.05
C385638		2.76	58.1	6.31	10.40	0.49	2.8	4.39	0.015	1.52	14.6	6.2	0.17	8	40.30	0.07
C385639		5.81	110.0	4.15	14.10	0.26	3.1	0.47	0.062	1.50	20.8	21.6	0.55	33	54.70	0.35

Comments: Interference: Mo>400ppm on ICP-MS Cd,ICP-AES results shown. REE's may not be totally soluble in MS61 method.

ALS Chemex
EXCELLENCE IN ANALYTICAL CHEMISTRY
ALS Canada Ltd.
212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: STRATEGIC METALS LTD.
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO

Finalized Date: 20-JUL-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07067539

Sample Description	Method / Analyte / Units / LOR	ME-MS61 Nb ppm 0.1	ME-MS61 Ni ppm 0.2	ME-MS61 P ppm 10	ME-MS61 Pb ppm 0.5	ME-MS61 Rb ppm 0.1	ME-MS61 Re ppm 0.002	ME-MS61 S % 0.01	ME-MS61 Sb ppm 0.05	ME-MS61 Sc ppm 0.1	ME-MS61 Se ppm 1	ME-MS61 Sn ppm 0.2	ME-MS61 Sr ppm 0.2	ME-MS61 Ta ppm 0.05	ME-MS61 Te ppm 0.05	ME-MS61 Th ppm 0.2
C385634		10.3	45.3	260	16.8	131.0	0.049	1.49	6.79	10.9	10	2.2	88.8	0.75	0.07	8.2
C385635		8.4	339.0	980	12.7	94.8	0.017	4.79	4.92	16.3	10	1.6	139.0	0.53	0.06	9.5
C385636		1.2	>10000	40	75.2	14.9	>50	>10.0	130.00	1.8	>1000	1.3	134.0	0.06	18.70	0.3
C385637		14.4	406.0	380	16.5	165.0	0.737	0.75	22.80	14.1	131	2.7	530.0	0.87	0.55	7.5
C385638		13.5	36.7	340	195.5	77.0	0.030	4.00	977.00	2.5	65	4.6	334.0	4.43	0.32	20.2
C385639		17.6	263.0	570	21.9	96.3	0.191	3.74	67.90	7.2	39	2.2	203.0	1.91	0.19	8.4

Comments: Interference: Mo>400ppm on ICP-MS Cd,ICP-AES results shown. REE's may not be totally soluble in MS61 method.

ALS Chemex
EXCELLENCE IN ANALYTICAL CHEMISTRY
ALS Canada Ltd.
212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

: STRATEGIC METALS LTD.
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO

Finalized Date: 20-JUL-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07067539

Sample Description	Method	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	Ni-AA62
	Analyte	Ti	Tl	U	V	W	Y	Zn	Zr	Ni
	Units	%	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%
	LOR	0.005	0.02	0.1	1	0.1	0.1	2	0.5	0.01
C385634		0.341	4.81	6.2	775	1.3	9.3	87	93.6	
C385635		0.252	2.62	16.2	499	0.9	42.3	564	70.7	
C385636		0.026	213.00	2.9	155	1.6	2.1	299	10.4	4.16
C385637		0.394	33.70	7.4	865	1.5	15.9	23	117.0	
C385638		0.116	6.28	4.6	1540	1.1	33.9	56	81.9	
C385639		0.228	3.16	9.3	1810	1.1	36.2	477	89.2	

Comments: Interference: Mo>400ppm on ICP-MS Cd,ICP-AES results shown. REE's may not be totally soluble in MS61 method.

ALS Chemex
EXCELLENCE IN ANALYTICAL CHEMISTRY
ALS Canada Ltd.
212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Finalized Date: 2-JUL-2007
Account: MTT

CERTIFICATE VA07064995

Project: NiMo

P.O. No.:

This report is for 253 Soil samples submitted to our lab in Vancouver, BC, Canada on 22-JUN-2007.

The following have access to data associated with this certificate:

JOAN MARIACHER

SAMPLE PREPARATION

ALS CODE	DESCRIPTION
WEI-21	Received Sample Weight
LOG-22	Sample login - Rcd w/o BarCode
SCR-41	Screen to -180um and save both

ANALYTICAL PROCEDURES

ALS CODE	DESCRIPTION	INSTRUMENT
ME-OG46	Ore Grade Elements - AquaRegia	ICP-AES
Zn-OG46	Ore Grade Zn - Aqua Regia	VARIABLE
ME-MS41	51 anal. aqua regia ICPMS	

To: **STRATEGIC METALS LTD.**
ATTN: JOAN MARIACHER
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

This is the Final Report and supersedes any preliminary report with this certificate number. Results apply to samples as submitted. All pages of this report have been checked and approved for release.

Signature: Lawrence Ng

Lawrence Ng, Laboratory Manager - Vancouver

ALS Chemex

EXCELLENCE IN ANALYTICAL CHEMISTRY

ALS Canada Ltd.

212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: STRATEGIC METALS LTD.
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NiMo

Finalized Date: 2-JUL-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07064995

Sample Description	Method	WEI-21	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41
	Analyte	Recvd Wt.	Ag	Al	As	Au	B	Ba	Be	Bi	Ca	Cd	Ce	Co	Cr	Cs
	Units	kg	ppm	%	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppm	ppm	ppm
	LOR	0.02	0.01	0.01	0.1	0.2	10	10	0.05	0.01	0.01	0.01	0.02	0.1	1	0.05
CC20196		0.08	0.92	0.34	41.8	<0.2	<10	760	0.75	0.15	4.95	14.35	23.70	13.9	22	0.89
CC20197		0.10	0.53	0.89	10.1	<0.2	10	2400	0.53	0.13	1.32	4.35	24.70	7.5	17	0.92
CC20198		0.10	0.55	1.89	13.2	<0.2	<10	1690	1.05	0.13	1.38	12.35	24.90	9.5	26	0.90
CC20199		0.16	0.31	9.37	24.1	<0.2	<10	550	6.07	0.11	0.92	15.05	13.95	8.1	75	0.78
CC20200		0.10	0.76	1.03	13.2	<0.2	<10	1590	0.75	0.18	1.23	18.15	23.30	19.2	18	0.94
CC20333		0.16	0.99	1.88	16.9	<0.2	<10	190	0.43	0.24	0.03	0.24	19.30	5.7	32	1.21
CC20334		0.08	1.27	0.70	8.0	<0.2	<10	220	0.17	0.20	0.03	0.24	16.35	1.5	13	0.87
CC20335		0.16	3.24	1.80	35.1	<0.2	<10	560	0.34	0.30	0.03	0.60	17.80	4.5	40	1.32
CC20336		0.18	0.89	1.84	38.9	<0.2	<10	510	0.52	0.24	0.05	0.48	21.40	8.5	38	1.10
CC20429		0.12	0.85	0.31	14.7	<0.2	<10	710	0.20	0.18	0.01	0.52	8.09	0.5	12	0.96
CC20430		0.10	0.31	1.43	33.6	<0.2	<10	180	0.27	0.33	0.02	0.41	15.50	3.4	26	1.06
CC20431		0.08	0.71	2.28	52.1	<0.2	<10	250	0.42	0.28	0.03	0.34	15.90	3.0	48	1.22
CC20432		0.10	0.51	0.77	11.0	<0.2	<10	140	0.14	0.25	0.02	0.13	22.40	3.2	14	0.83
CC20433		0.10	0.21	1.62	15.4	<0.2	<10	140	0.33	0.25	0.02	0.12	18.05	5.4	25	1.23
CC20434		0.08	0.33	0.89	23.4	<0.2	<10	180	0.29	0.24	0.01	0.20	12.15	2.2	22	1.11
CC20435		0.10	0.54	1.67	19.4	<0.2	<10	190	0.36	0.25	0.04	0.62	19.20	6.1	25	1.17
CC20436		0.18	0.16	0.40	15.2	<0.2	<10	800	0.40	0.11	0.10	1.38	8.35	1.8	11	0.36
CC20437		0.20	0.16	0.49	8.8	<0.2	<10	410	0.24	0.11	0.02	0.58	9.24	2.3	9	0.52
CC20438		0.14	0.04	0.97	15.1	<0.2	<10	140	0.21	0.18	0.02	0.19	15.90	3.5	16	0.88
CC20439		0.16	1.26	1.16	21.6	<0.2	<10	3710	0.86	0.21	0.21	9.70	31.50	12.1	29	0.60
CC20440		0.10	0.22	1.25	10.9	<0.2	<10	1840	0.66	0.22	0.12	1.00	27.40	12.4	21	0.58
CC20441		0.14	0.10	0.81	12.3	<0.2	<10	170	0.16	0.19	0.04	0.24	18.55	3.1	14	0.79
CC20442		0.14	0.11	1.16	16.9	<0.2	<10	320	0.31	0.19	0.02	0.55	16.25	4.9	21	0.67
CC20443		0.12	0.37	2.37	34.1	<0.2	<10	500	0.62	0.25	0.04	0.86	20.10	9.3	37	1.20
CC20444		0.10	0.74	1.13	36.3	<0.2	<10	410	0.30	0.25	0.02	0.41	14.50	2.9	25	0.88
CC20445		0.12	0.77	0.73	29.7	<0.2	<10	270	0.17	0.26	0.03	0.16	16.75	2.4	18	1.07
CC20446		0.10	0.50	0.80	17.4	<0.2	<10	160	0.12	0.29	0.08	0.09	17.75	3.0	15	0.70
CC20447		0.12	0.39	1.43	17.3	<0.2	<10	190	0.26	0.27	0.04	0.20	19.45	3.9	22	1.05
CC20451		0.04	0.53	0.53	8.4	<0.2	10	1080	0.43	0.09	4.08	2.64	10.55	2.6	12	0.45
CC20452		0.10	0.64	0.54	15.4	<0.2	10	1230	0.48	0.09	3.51	1.62	11.90	3.4	14	0.24
CC20453		0.08	0.71	0.65	24.5	<0.2	<10	1700	0.60	0.22	1.45	7.39	17.95	3.2	23	0.61
CC20454		0.10	0.28	1.85	16.2	<0.2	<10	250	0.31	0.28	0.04	0.11	18.15	5.9	27	1.06
CC20455		0.12	0.24	0.75	16.4	<0.2	<10	190	0.15	0.24	0.04	0.08	20.50	3.1	16	0.76
CC20456		0.12	0.42	2.04	22.5	<0.2	<10	200	0.43	0.25	0.04	0.15	21.60	7.5	32	1.22
CC20457		0.08	0.92	0.99	48.0	<0.2	<10	410	0.36	0.30	0.03	0.65	18.35	3.0	28	1.08
CC20458		0.14	0.44	0.38	24.6	<0.2	<10	1300	0.36	0.18	0.08	4.64	10.35	1.1	20	0.75
CC20459		0.32	1.11	1.03	10.8	<0.2	<10	1070	0.48	0.23	0.17	2.60	21.40	1.9	22	0.87
CC20460		0.16	1.14	0.71	16.7	<0.2	<10	1470	0.47	0.17	0.98	7.50	16.40	6.8	19	0.53
CC20461		0.14	0.72	0.81	7.0	<0.2	<10	1420	0.32	0.19	1.13	0.42	19.25	18.1	12	0.53
CC20462		0.08	0.49	0.89	20.3	<0.2	<10	1450	0.55	0.20	1.35	1.32	48.00	98.4	12	0.55

Comments: Gold determinations by ME-MS41 are semi-quantitative due to the small sample weight used (0.5g).

ALS Chemex

EXCELLENCE IN ANALYTICAL CHEMISTRY

ALS Canada Ltd.

212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: STRATEGIC METALS LTD.
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NiMo

Finalized Date: 2-JUL-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07064995

Sample Description	Method	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41
	Analyte	Cu	Fe	Ga	Ge	Hf	Hg	In	K	La	Li	Mg	Mn	Mo	Na	Nb
	Units	ppm	%	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	%	ppm	ppm	%	ppm
	LOR	0.2	0.01	0.05	0.05	0.02	0.01	0.005	0.01	0.2	0.1	0.01	5	0.05	0.01	0.05
CC20196		82.6	2.28	1.78	0.11	0.23	0.21	0.039	0.09	13.1	2.1	1.17	225	53.10	0.02	0.12
CC20197		49.7	1.84	2.40	0.06	0.12	0.17	0.025	0.12	14.4	8.4	0.58	186	6.21	0.02	0.18
CC20198		157.0	2.21	2.65	0.07	0.18	0.16	0.035	0.12	14.2	8.9	0.61	194	8.67	0.02	0.21
CC20199		504.0	2.55	3.75	0.08	0.29	0.09	0.059	0.06	6.8	7.2	0.25	126	11.20	0.01	0.13
CC20200		174.5	2.93	2.64	0.07	0.13	0.20	0.034	0.09	13.6	10.9	0.39	282	7.55	0.02	0.26
CC20333		16.5	3.46	6.65	0.06	0.06	0.07	0.034	0.07	10.3	23.9	0.25	161	14.25	0.01	1.24
CC20334		14.6	1.24	4.55	<0.05	<0.02	0.03	0.012	0.04	8.8	1.0	0.04	41	10.10	0.01	0.43
CC20335		22.1	3.94	7.04	0.11	0.07	0.07	0.047	0.21	12.0	16.0	0.21	126	40.50	0.01	0.84
CC20336		27.4	3.43	5.86	0.09	0.06	0.07	0.045	0.14	11.5	18.4	0.33	189	44.80	0.01	0.71
CC20429		44.7	1.40	1.31	0.06	0.03	0.04	0.026	0.13	4.3	0.9	0.01	15	54.40	0.01	0.09
CC20430		13.5	3.21	8.34	0.05	<0.02	0.05	0.027	0.06	8.3	5.6	0.09	124	29.90	0.01	1.03
CC20431		14.7	2.72	6.61	0.06	0.06	0.07	0.035	0.05	8.6	10.6	0.08	80	48.80	0.01	1.03
CC20432		10.9	2.02	6.50	<0.05	<0.02	0.04	0.015	0.03	11.7	3.2	0.06	102	16.25	<0.01	0.84
CC20433		17.8	3.45	7.10	0.06	0.07	0.03	0.036	0.05	9.4	19.9	0.16	104	13.55	<0.01	1.22
CC20434		17.5	2.76	4.48	0.06	0.05	0.07	0.030	0.07	7.2	5.9	0.09	61	42.60	<0.01	0.75
CC20435		15.2	3.27	6.76	0.06	0.08	0.05	0.031	0.06	10.1	19.3	0.26	181	14.50	0.01	1.20
CC20436		34.1	0.85	1.33	<0.05	0.03	0.05	0.020	0.07	4.9	1.7	0.03	23	17.10	0.01	0.11
CC20437		24.7	1.03	1.74	<0.05	0.03	0.03	0.018	0.05	5.3	1.3	0.03	20	17.65	0.01	0.14
CC20438		11.3	2.42	4.35	<0.05	0.08	0.01	0.024	0.05	8.3	8.1	0.12	91	16.30	<0.01	0.72
CC20439		70.3	2.88	2.65	0.08	0.12	0.18	0.040	0.09	15.8	7.3	0.12	222	19.95	0.03	0.28
CC20440		31.2	2.63	3.60	0.06	0.06	0.05	0.032	0.08	14.1	15.5	0.26	240	7.58	0.02	0.43
CC20441		7.8	1.93	4.98	<0.05	<0.02	0.01	0.015	0.04	9.5	5.7	0.12	95	9.77	<0.01	0.79
CC20442		16.1	2.34	3.96	0.05	0.03	0.01	0.027	0.07	8.7	10.7	0.19	98	19.65	0.01	0.57
CC20443		26.9	3.26	5.84	0.07	0.15	0.05	0.048	0.10	10.9	26.6	0.30	185	28.50	0.01	0.77
CC20444		17.1	2.92	6.08	0.08	0.04	0.02	0.040	0.09	8.1	9.6	0.13	99	74.60	0.01	0.89
CC20445		11.0	2.57	6.95	0.07	<0.02	0.03	0.025	0.07	9.4	2.9	0.07	58	45.30	<0.01	0.95
CC20446		10.0	2.71	7.34	0.05	0.02	0.03	0.018	0.05	9.2	3.8	0.10	122	28.50	<0.01	1.27
CC20447		13.2	3.38	8.59	0.05	0.08	0.03	0.027	0.05	10.2	11.0	0.15	112	25.20	<0.01	1.27
CC20451		31.8	1.19	1.68	0.05	0.09	0.08	0.021	0.04	6.6	3.4	0.18	117	6.39	0.02	0.19
CC20452		29.1	1.34	1.71	0.06	0.08	0.09	0.021	0.05	7.3	4.3	0.20	98	11.55	0.02	0.19
CC20453		48.4	1.95	3.05	0.08	0.08	0.06	0.046	0.07	11.4	1.8	0.09	35	15.70	0.02	0.22
CC20454		14.0	3.75	7.61	0.07	0.05	0.03	0.034	0.05	9.3	24.7	0.24	196	12.15	0.01	1.24
CC20455		16.1	2.52	7.27	0.05	<0.02	0.04	0.020	0.04	10.7	3.8	0.08	76	28.00	<0.01	1.04
CC20456		35.4	3.41	6.72	0.06	0.06	0.04	0.038	0.06	11.1	22.0	0.26	161	12.80	0.01	1.20
CC20457		27.0	3.35	6.86	0.10	0.02	0.07	0.037	0.10	10.4	5.0	0.11	114	79.00	0.01	0.84
CC20458		64.8	1.25	1.66	0.08	0.02	0.17	0.029	0.11	5.6	0.8	0.02	14	58.70	0.02	0.10
CC20459		34.8	1.09	3.59	0.06	0.05	0.45	0.035	0.07	12.7	8.0	0.13	27	11.15	0.01	0.37
CC20460		38.3	1.64	2.50	0.05	0.07	0.31	0.025	0.07	9.2	6.1	0.12	315	19.75	0.02	0.30
CC20461		18.0	3.26	2.17	0.06	0.09	0.14	0.022	0.07	9.7	6.1	0.23	807	1.70	0.02	0.24
CC20462		22.7	7.85	2.72	0.11	0.12	0.10	0.026	0.05	14.9	7.2	0.22	6180	4.28	0.02	0.32

Comments: Gold determinations by ME-MS41 are semi-quantitative due to the small sample weight used (0.5g).

ALS Chemex

EXCELLENCE IN ANALYTICAL CHEMISTRY

ALS Canada Ltd.

212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: STRATEGIC METALS LTD.
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NiMo

Finalized Date: 2-JUL-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07064995

Sample Description	Method	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41
	Analyte	Ni	P	Pb	Rb	Re	S	Sb	Sc	Se	Sn	Sr	Ta	Te	Th	Ti
	Units	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%
	LOR	0.2	10	0.2	0.1	0.001	0.01	0.05	0.1	0.2	0.2	0.2	0.01	0.01	0.2	0.005
CC20196		198.0	840	11.3	7.5	0.070	0.33	10.35	5.6	13.2	0.6	244.0	0.01	0.13	4.1	<0.005
CC20197		55.0	1170	8.9	9.6	0.027	0.10	2.70	3.6	3.6	0.3	111.5	<0.01	0.04	2.8	0.005
CC20198		82.3	1590	8.8	9.5	0.030	0.19	3.06	4.7	4.6	0.4	121.5	<0.01	0.05	3.3	0.005
CC20199		86.9	2070	6.7	6.5	0.015	0.62	3.04	12.3	6.1	0.3	87.7	0.01	0.06	2.4	<0.005
CC20200		164.5	930	10.9	9.3	0.019	0.17	2.89	4.3	5.8	0.4	92.3	<0.01	0.06	2.4	0.005
CC20333		16.9	410	13.3	13.8	<0.001	0.03	9.32	3.1	4.5	0.8	10.5	<0.01	0.10	3.2	0.018
CC20334		6.3	380	12.0	6.1	<0.001	0.03	3.64	0.8	3.2	0.8	7.4	<0.01	0.08	0.3	0.014
CC20335		14.1	850	19.8	20.8	0.001	0.35	19.80	3.8	20.6	1.1	32.5	<0.01	0.25	3.3	0.012
CC20336		26.1	930	13.4	14.6	0.001	0.20	11.90	4.0	11.3	0.9	26.2	<0.01	0.16	2.9	0.016
CC20429		6.6	360	12.8	10.1	0.002	0.41	5.87	1.4	7.9	0.5	42.1	<0.01	0.11	1.1	<0.005
CC20430		18.8	750	16.6	8.3	0.001	0.05	6.89	1.3	4.2	1.0	10.5	<0.01	0.15	0.3	0.025
CC20431		17.0	1760	15.3	9.4	0.001	0.07	12.35	2.8	7.5	0.9	9.0	0.01	0.19	1.7	0.017
CC20432		10.1	220	10.1	6.1	<0.001	0.01	4.07	1.4	1.8	0.9	5.5	<0.01	0.10	1.3	0.032
CC20433		17.3	270	12.3	11.5	<0.001	0.01	3.06	2.7	3.1	0.8	6.5	<0.01	0.10	3.0	0.023
CC20434		7.6	430	9.6	12.5	0.001	0.03	17.05	2.0	8.1	0.7	8.7	<0.01	0.27	2.2	0.012
CC20435		16.9	400	13.5	11.0	<0.001	0.02	4.98	2.7	3.0	0.7	11.2	<0.01	0.10	3.0	0.023
CC20436		46.6	270	5.7	5.6	0.037	0.07	4.35	1.8	5.1	0.4	26.7	<0.01	0.08	1.5	<0.005
CC20437		34.3	290	6.3	6.6	0.010	0.03	3.01	1.4	2.6	0.4	15.1	<0.01	0.05	0.8	<0.005
CC20438		29.9	180	9.2	10.6	0.001	<0.01	2.83	1.8	2.1	0.6	8.8	<0.01	0.07	2.7	0.015
CC20439		94.2	500	13.9	8.6	0.001	0.02	9.71	5.2	6.1	0.5	19.5	<0.01	0.09	4.1	0.006
CC20440		37.1	510	11.1	8.6	<0.001	0.01	1.88	3.1	1.3	0.4	13.2	<0.01	0.06	2.5	0.011
CC20441		16.5	240	8.2	9.4	<0.001	<0.01	1.71	1.6	1.2	0.6	8.6	<0.01	0.05	1.5	0.021
CC20442		41.5	280	10.9	10.6	0.002	0.03	4.16	2.5	3.6	0.6	27.3	<0.01	0.08	2.5	0.012
CC20443		48.2	430	14.1	16.7	0.001	0.06	9.10	3.8	7.5	0.8	26.6	<0.01	0.14	4.9	0.014
CC20444		11.6	630	13.9	12.7	<0.001	0.12	19.50	2.2	13.8	0.9	28.9	<0.01	0.26	2.3	0.016
CC20445		8.5	540	15.0	9.9	<0.001	0.07	15.00	1.6	8.5	0.9	24.2	<0.01	0.22	1.6	0.026
CC20446		10.4	250	10.9	8.4	<0.001	0.01	5.63	1.6	3.4	0.8	11.0	<0.01	0.11	2.0	0.034
CC20447		12.9	280	13.5	7.4	<0.001	0.01	3.47	2.3	2.7	0.9	10.2	<0.01	0.10	2.9	0.024
CC20451		50.7	880	6.6	4.2	0.004	0.20	3.10	1.6	5.3	0.3	146.5	<0.01	0.07	0.6	0.005
CC20452		40.7	900	7.3	4.0	0.002	0.18	4.87	1.3	6.6	0.4	146.5	<0.01	0.10	0.5	0.005
CC20453		71.7	690	15.1	8.6	0.002	0.10	5.71	2.5	9.4	1.0	72.7	<0.01	0.26	1.2	0.005
CC20454		15.8	350	15.5	8.0	<0.001	0.02	1.53	3.1	2.6	0.9	8.2	<0.01	0.07	2.8	0.026
CC20455		9.3	230	10.9	8.8	<0.001	0.01	5.58	1.5	5.2	0.8	6.5	<0.01	0.10	2.0	0.035
CC20456		23.5	280	12.2	12.6	0.001	0.01	3.63	3.8	4.8	0.7	8.2	<0.01	0.10	3.7	0.030
CC20457		9.1	780	16.9	13.2	0.001	0.13	17.90	2.3	17.7	0.9	30.9	<0.01	0.24	2.0	0.023
CC20458		30.2	840	12.9	8.2	0.024	0.23	9.43	1.7	11.0	0.6	76.1	<0.01	0.21	0.5	<0.005
CC20459		33.8	420	16.3	11.0	0.024	0.04	4.83	3.4	8.9	0.7	43.6	<0.01	0.09	2.5	0.006
CC20460		49.8	700	10.0	8.2	0.019	0.07	5.74	3.0	5.3	0.5	82.3	<0.01	0.08	1.5	0.006
CC20461		16.4	940	10.3	9.7	0.004	0.11	0.59	2.6	2.3	0.2	51.3	<0.01	0.05	2.0	0.005
CC20462		26.2	1010	9.6	8.7	0.003	0.12	0.79	3.2	2.5	0.2	59.0	<0.01	0.08	2.3	0.008

Comments: Gold determinations by ME-MS41 are semi-quantitative due to the small sample weight used (0.5g).

ALS Chemex
EXCELLENCE IN ANALYTICAL CHEMISTRY
ALS Canada Ltd.
212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: STRATEGIC METALS LTD.
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NiMo

CERTIFICATE OF ANALYSIS VA07064995

Sample Description	Method	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	Zn-OG46
	Analyte	Tl	U	V	W	Y	Zn	Zr	Zn
	Units	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%
	LOR	0.02	0.05	1	0.05	0.05	2	0.5	0.01
CC20196		1.71	11.65	301	0.25	33.20	1040	10.8	
CC20197		0.44	3.03	97	0.06	15.75	389	3.2	
CC20198		0.64	6.13	185	0.09	23.60	549	4.7	
CC20199		0.58	27.80	506	0.09	51.20	914	7.0	
CC20200		0.65	4.11	105	0.08	20.80	617	3.5	
CC20333		0.62	0.77	174	0.20	2.67	56	1.8	
CC20334		0.62	0.81	120	0.14	1.50	25	<0.5	
CC20335		4.00	1.74	304	0.24	3.36	51	2.4	
CC20336		3.08	3.28	268	0.26	6.19	64	1.4	
CC20429		5.28	5.42	134	0.24	5.67	21	0.8	
CC20430		1.10	1.81	423	0.28	2.69	58	<0.5	
CC20431		1.47	8.03	350	0.29	3.47	41	1.5	
CC20432		0.45	0.67	200	0.19	2.00	34	<0.5	
CC20433		0.48	0.79	145	0.19	2.37	58	2.3	
CC20434		1.71	1.65	248	0.25	2.94	27	1.8	
CC20435		0.71	0.91	154	0.24	2.69	61	2.1	
CC20436		1.58	3.35	85	0.09	6.00	125	0.8	
CC20437		0.92	2.89	69	0.11	5.10	73	0.5	
CC20438		0.76	0.85	131	0.14	2.43	89	2.9	
CC20439		0.21	3.57	237	0.13	19.65	438	3.2	
CC20440		0.13	1.19	77	0.18	10.55	169	0.9	
CC20441		0.44	0.37	114	0.16	1.84	67	<0.5	
CC20442		1.11	1.20	135	0.15	3.67	116	1.0	
CC20443		2.41	2.26	212	0.20	4.83	126	5.1	
CC20444		3.69	2.92	371	0.33	5.17	43	1.5	
CC20445		2.05	1.41	294	0.30	2.91	36	<0.5	
CC20446		0.57	0.58	227	0.23	1.88	44	0.6	
CC20447		0.78	0.78	245	0.21	2.23	51	2.6	
CC20451		0.72	2.45	73	0.07	9.37	189	2.5	
CC20452		0.66	4.94	113	0.10	9.94	134	2.1	
CC20453		1.65	4.76	160	0.24	12.10	254	2.2	
CC20454		0.42	0.61	130	0.19	2.18	54	1.9	
CC20455		0.34	0.62	316	0.19	1.97	36	<0.5	
CC20456		0.34	1.25	235	0.19	3.75	57	2.1	
CC20457		2.75	4.81	494	0.28	5.05	33	0.7	
CC20458		6.36	11.55	154	0.20	8.74	69	<0.5	
CC20459		2.22	4.41	155	0.13	10.25	146	1.2	
CC20460		0.68	4.34	258	0.12	11.70	407	1.9	
CC20461		0.09	0.83	43	0.07	9.18	72	1.9	
CC20462		0.09	1.08	45	0.11	14.55	105	2.4	

Comments: Gold determinations by ME-MS41 are semi-quantitative due to the small sample weight used (0.5g).

ALS Chemex

EXCELLENCE IN ANALYTICAL CHEMISTRY

ALS Canada Ltd.

212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: STRATEGIC METALS LTD.
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NiMo

Finalized Date: 2-JUL-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07064995

Sample Description	Method	WEI-21	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41
	Analyte	Recvd Wt.	Ag	Al	As	Au	B	Ba	Be	Bi	Ca	Cd	Ce	Co	Cr	Cs
	Units	kg	ppm	%	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppm	ppm	ppm
	LOR	0.02	0.01	0.01	0.1	0.2	10	10	0.05	0.01	0.01	0.01	0.02	0.1	1	0.05
CC20466		0.04	0.55	0.66	16.7	<0.2	<10	1280	0.40	0.12	2.68	3.27	11.95	6.8	15	0.51
CC20467		0.06	0.43	0.52	13.8	<0.2	<10	1370	0.42	0.10	2.69	1.30	12.20	3.6	11	0.39
CC20468		0.06	0.51	0.67	18.5	<0.2	<10	1380	0.42	0.11	2.89	1.81	12.90	8.3	14	0.51
CC20469		0.06	0.44	0.58	19.5	<0.2	<10	1790	0.52	0.10	2.98	3.59	11.45	22.9	10	0.39
CC20470		0.06	0.53	0.51	14.0	<0.2	<10	1650	0.35	0.12	0.83	2.15	9.39	2.9	16	0.56
CC20471		0.10	0.51	0.84	15.7	<0.2	<10	1610	0.54	0.19	1.28	7.26	13.65	4.0	25	0.80
CC20472		0.08	0.50	1.19	17.5	<0.2	<10	1400	0.57	0.18	0.90	5.93	15.75	6.2	34	0.78
CC20473		0.08	0.63	0.93	11.2	<0.2	10	1800	0.80	0.17	2.09	8.18	17.65	6.5	29	0.83
CC20474		0.10	0.99	1.13	12.0	<0.2	10	820	0.81	0.14	3.75	2.63	32.90	8.2	28	0.90
CC20475		0.10	0.55	1.07	9.7	<0.2	<10	1750	0.74	0.12	2.59	0.80	24.50	7.5	19	0.59
CC20476		0.10	0.64	1.19	9.4	<0.2	10	950	0.73	0.15	2.25	1.67	31.70	7.9	23	0.78
CC20477		0.10	0.39	0.71	7.2	<0.2	<10	2520	0.58	0.11	2.94	1.20	12.40	9.5	13	0.34
CC20478		0.04	0.47	1.61	7.8	<0.2	<10	1020	0.78	0.21	0.41	0.23	32.70	14.7	22	1.00
CC20479		0.06	0.24	1.05	2.6	<0.2	<10	390	0.29	0.15	0.18	0.17	25.80	4.8	16	0.70
CC20480		0.12	0.10	1.07	3.4	<0.2	<10	390	0.36	0.16	0.15	0.22	27.70	4.0	17	0.62
CC20481		0.08	0.27	1.21	2.6	<0.2	<10	680	0.50	0.15	0.25	0.13	32.00	4.7	18	0.70
CC20482		0.12	0.28	1.58	4.2	<0.2	<10	860	0.83	0.27	0.23	0.15	38.30	9.9	23	0.90
CC20483		0.08	0.30	1.35	4.6	<0.2	<10	730	0.50	0.21	0.33	0.20	28.60	5.7	20	0.82
CC20484		0.10	0.19	1.34	3.9	<0.2	<10	650	0.64	0.19	0.12	0.21	35.20	5.4	20	0.79
CC20485		0.08	0.41	1.08	2.5	<0.2	<10	850	0.54	0.16	0.21	0.21	30.50	7.4	16	0.73
CC20486		0.12	0.60	1.11	6.9	<0.2	<10	1230	0.84	0.21	0.50	0.28	37.00	18.6	16	0.66
CC20487		0.12	0.45	1.36	3.4	<0.2	<10	860	0.59	0.20	0.32	0.12	34.60	5.3	20	0.86
CC20488		0.10	0.49	1.36	16.4	<0.2	<10	420	0.82	0.14	2.28	1.63	35.80	9.8	25	0.86
CC20489		0.14	2.50	0.69	14.5	<0.2	<10	580	0.55	0.23	0.17	5.43	16.80	1.4	26	0.79
CC20490		0.14	3.28	0.39	8.0	<0.2	<10	380	0.29	0.18	0.02	0.93	9.03	0.2	17	0.63
CC20491		0.18	1.00	2.17	110.5	<0.2	<10	720	2.43	0.18	0.09	49.70	19.00	20.8	70	0.72
CC20492		0.16	1.04	0.84	17.2	<0.2	<10	940	0.84	0.21	0.53	7.43	14.15	2.2	20	0.34
CC20493		0.22	0.31	0.43	6.8	<0.2	<10	580	0.30	0.18	0.04	0.93	6.84	0.6	9	0.60
CC20494		0.12	0.39	0.41	25.4	<0.2	<10	1000	0.53	0.16	0.41	0.97	8.46	3.0	10	0.48
CC29501		0.18	0.29	1.55	46.1	<0.2	<10	340	0.52	0.25	0.03	0.26	20.10	6.0	29	1.23
CC29502		0.14	0.10	0.63	24.7	<0.2	<10	170	0.18	0.20	0.03	0.13	17.95	2.4	13	0.89
CC29503		0.14	0.29	1.62	20.5	<0.2	<10	230	0.46	0.22	0.05	0.43	18.35	5.4	25	1.17
CC29504		0.18	2.62	1.20	36.3	<0.2	<10	1040	0.97	0.18	2.34	23.50	18.75	5.6	27	1.72
CC29505		0.06	0.24	0.13	3.1	<0.2	10	210	0.09	0.02	2.92	3.82	1.85	0.6	6	0.22
CC29506		0.12	2.51	0.68	40.6	<0.2	10	1260	0.94	0.14	2.52	18.05	25.50	6.2	64	0.75
CC29507		0.10	1.35	0.49	24.2	<0.2	10	880	0.66	0.09	3.49	22.80	17.45	2.6	33	0.56
CC29508		0.14	1.41	0.47	18.6	<0.2	10	730	0.67	0.10	2.74	18.65	17.60	4.5	33	0.59
CC29509		0.08	0.30	0.17	4.4	<0.2	10	550	0.18	0.02	3.10	9.18	4.22	0.8	6	0.20
CC29510		0.16	0.75	0.57	15.4	<0.2	10	930	0.65	0.07	3.38	11.80	17.25	3.4	15	0.48
CC29511		0.08	0.50	0.34	9.9	<0.2	10	790	0.50	0.37	2.95	11.25	7.59	4.5	5	0.20

Comments: Gold determinations by ME-MS41 are semi-quantitative due to the small sample weight used (0.5g).

ALS Chemex

EXCELLENCE IN ANALYTICAL CHEMISTRY

ALS Canada Ltd.

212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: STRATEGIC METALS LTD.
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NiMo

Finalized Date: 2-JUL-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07064995

Sample Description	Method	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41
	Analyte	Cu	Fe	Ga	Ge	Hf	Hg	In	K	La	Li	Mg	Mn	Mo	Na	Nb
	Units	ppm	%	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	%	ppm	ppm	%	ppm
	LOR	0.2	0.01	0.05	0.05	0.02	0.01	0.005	0.01	0.2	0.1	0.01	5	0.05	0.01	0.05
CC20466		24.6	1.63	2.13	0.05	0.10	0.09	0.026	0.05	6.3	6.1	0.20	485	9.42	0.02	0.25
CC20467		25.7	1.40	1.63	0.05	0.09	0.09	0.020	0.04	6.9	2.8	0.10	171	5.66	0.02	0.18
CC20468		22.4	1.55	2.12	<0.05	0.09	0.11	0.020	0.04	6.7	6.2	0.23	675	6.49	0.02	0.24
CC20469		33.7	2.02	1.45	0.05	0.11	0.10	0.021	0.04	6.2	2.9	0.15	1200	9.08	0.03	0.15
CC20470		24.2	1.71	1.90	0.05	0.05	0.11	0.019	0.05	5.4	1.7	0.06	43	16.00	0.02	0.15
CC20471		42.5	1.59	3.03	0.06	0.09	0.12	0.032	0.05	8.0	3.8	0.13	45	4.51	0.02	0.24
CC20472		36.2	2.03	4.74	0.05	0.10	0.04	0.027	0.05	8.9	8.6	0.31	91	3.56	0.02	0.48
CC20473		47.1	1.96	3.41	0.05	0.11	0.06	0.027	0.09	10.3	6.6	0.25	189	4.17	0.02	0.29
CC20474		48.0	1.76	3.76	0.08	0.14	0.14	0.026	0.12	19.0	19.3	1.16	248	6.00	0.02	0.44
CC20475		30.7	1.64	3.41	0.06	0.12	0.11	0.024	0.05	15.3	13.5	0.46	248	2.94	0.02	0.35
CC20476		35.4	1.91	3.81	0.06	0.17	0.09	0.028	0.10	17.4	20.7	0.89	208	4.03	0.02	0.55
CC20477		33.7	1.61	1.72	0.05	0.11	0.09	0.023	0.06	7.0	5.9	0.23	152	2.24	0.03	0.17
CC20478		32.7	3.58	4.90	0.06	0.06	0.10	0.030	0.07	16.7	14.0	0.28	229	1.41	0.02	0.48
CC20479		10.1	1.58	3.79	0.05	0.03	0.08	0.015	0.07	13.0	10.0	0.23	89	0.55	0.01	0.39
CC20480		10.9	1.64	3.63	0.05	0.03	0.08	0.018	0.06	14.0	10.0	0.24	62	0.54	0.01	0.40
CC20481		20.3	1.62	3.86	0.05	0.05	0.10	0.023	0.07	16.1	13.0	0.28	65	0.32	0.01	0.40
CC20482		29.8	2.60	4.91	0.06	0.07	0.11	0.035	0.08	19.5	19.4	0.30	108	0.67	0.01	0.49
CC20483		20.0	2.20	4.21	0.06	0.05	0.11	0.027	0.08	14.4	13.0	0.26	81	0.78	0.01	0.44
CC20484		23.4	2.02	4.09	0.06	0.06	0.09	0.025	0.07	17.7	12.0	0.29	78	0.68	0.01	0.44
CC20485		18.6	1.76	3.50	0.05	0.05	0.08	0.021	0.06	15.5	8.0	0.24	100	0.63	0.01	0.31
CC20486		34.5	3.16	3.24	0.07	0.09	0.13	0.030	0.05	18.7	9.0	0.21	350	1.26	0.02	0.32
CC20487		27.0	2.34	4.12	0.06	0.06	0.12	0.028	0.07	17.8	13.0	0.29	75	0.56	0.01	0.39
CC20488		48.0	2.84	4.46	0.07	0.17	0.09	0.025	0.09	19.8	21.9	0.98	432	2.26	0.02	0.75
CC20489		54.9	1.16	2.65	0.13	0.04	0.09	0.038	0.14	12.9	1.2	0.03	112	27.20	0.01	0.13
CC20490		50.4	0.83	1.55	0.09	0.02	0.13	0.020	0.11	7.7	0.7	0.02	<5	34.20	0.01	0.11
CC20491		286.0	3.96	6.04	0.21	0.29	0.17	0.097	0.09	10.4	2.8	0.02	494	65.00	0.01	0.15
CC20492		78.0	1.11	2.80	0.09	0.09	0.15	0.040	0.09	8.8	3.0	0.03	43	35.90	0.01	0.16
CC20493		30.9	0.55	1.91	<0.05	0.02	0.04	0.015	0.07	4.3	0.8	0.02	16	21.80	0.01	0.13
CC20494		35.1	1.20	1.46	0.07	0.03	0.11	0.022	0.08	5.0	1.6	0.03	52	36.70	0.01	0.09
CC29501		45.0	3.61	5.84	0.12	0.04	0.05	0.040	0.12	10.6	12.0	0.22	130	57.30	0.01	0.72
CC29502		19.5	2.14	4.79	0.06	<0.02	0.02	0.020	0.08	9.6	1.9	0.05	50	34.10	0.01	0.66
CC29503		24.4	3.06	5.97	0.05	0.03	0.06	0.031	0.09	9.5	13.0	0.20	131	23.40	0.01	0.97
CC29504		83.9	1.73	4.09	0.09	0.21	0.51	0.031	0.10	12.3	7.6	0.11	96	24.40	0.02	0.56
CC29505		11.5	0.18	0.43	<0.05	0.03	0.11	<0.005	0.03	1.0	0.5	0.11	14	5.10	0.02	0.05
CC29506		80.3	1.27	3.08	0.12	0.18	0.57	0.021	0.06	15.8	4.8	0.25	75	35.50	0.02	0.24
CC29507		65.4	0.75	1.95	0.10	0.14	0.37	0.014	0.04	11.1	3.1	0.23	34	22.80	0.02	0.17
CC29508		68.0	0.83	1.83	0.09	0.13	0.39	0.015	0.05	11.6	3.4	0.18	163	13.75	0.02	0.19
CC29509		19.0	0.22	0.58	<0.05	0.05	0.13	<0.005	0.03	2.7	0.7	0.20	33	27.20	0.02	0.08
CC29510		51.1	0.88	1.72	0.10	0.14	0.20	0.013	0.04	11.4	3.5	0.13	90	12.00	0.02	0.23
CC29511		37.3	0.66	0.61	0.06	0.08	0.11	0.006	0.02	5.1	1.0	0.09	507	12.50	0.02	0.10

Comments: Gold determinations by ME-MS41 are semi-quantitative due to the small sample weight used (0.5g).

ALS Chemex

EXCELLENCE IN ANALYTICAL CHEMISTRY

ALS Canada Ltd.

212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NiMo

CERTIFICATE OF ANALYSIS VA07064995

Sample Description	Method	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41
	Analyte	Ni	P	Pb	Rb	Re	S	Sb	Sc	Se	Sn	Sr	Ta	Te	Th	Ti
	Units	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%
	LOR	0.2	10	0.2	0.1	0.001	0.01	0.05	0.1	0.2	0.2	0.2	0.01	0.01	0.2	0.005
CC20466		34.6	820	8.7	6.9	0.004	0.16	3.45	2.3	4.8	0.4	112.0	<0.01	0.10	1.1	0.006
CC20467		30.9	790	7.1	4.5	0.003	0.18	3.00	1.9	4.1	0.3	111.5	<0.01	0.08	0.8	0.005
CC20468		31.3	870	7.2	5.6	0.003	0.15	2.68	2.2	3.6	0.3	115.0	<0.01	0.07	0.9	0.005
CC20469		55.3	1090	6.5	6.4	0.003	0.21	2.93	1.9	4.4	0.3	129.0	<0.01	0.07	0.7	<0.005
CC20470		29.9	1130	6.0	8.2	0.006	0.14	2.56	2.2	5.0	0.4	46.4	<0.01	0.06	0.8	<0.005
CC20471		58.8	660	12.1	7.4	0.004	0.10	3.36	2.9	5.5	0.5	64.8	<0.01	0.10	1.2	<0.005
CC20472		55.0	620	12.4	5.9	0.001	0.06	3.27	3.4	3.0	0.7	41.8	<0.01	0.10	1.6	0.009
CC20473		77.7	730	10.1	11.7	0.001	0.07	3.31	3.3	2.6	0.5	82.7	<0.01	0.08	1.3	0.007
CC20474		50.4	1890	9.6	12.3	0.001	0.06	3.36	4.0	3.1	0.4	114.5	<0.01	0.07	2.5	0.013
CC20475		29.1	990	8.8	6.0	0.001	0.10	2.04	2.8	2.9	0.4	101.0	<0.01	0.05	1.1	0.007
CC20476		37.6	1140	9.3	11.0	0.001	0.05	2.30	4.1	1.9	0.4	76.7	<0.01	0.05	3.5	0.017
CC20477		35.2	810	6.3	5.5	0.002	0.13	1.60	2.5	2.9	0.2	140.5	<0.01	0.05	0.8	<0.005
CC20478		24.3	760	10.5	11.8	0.003	0.08	0.50	3.9	1.7	0.4	26.5	<0.01	0.04	2.4	0.006
CC20479		11.4	430	5.7	12.2	<0.001	0.03	0.25	2.5	1.0	0.3	14.3	<0.01	0.03	2.4	0.008
CC20480		12.6	420	7.6	11.5	<0.001	0.03	0.26	2.1	0.9	0.3	13.4	<0.01	0.03	1.9	0.008
CC20481		17.1	510	8.9	11.5	0.001	0.04	0.33	3.3	1.2	0.3	18.5	<0.01	0.03	2.9	0.008
CC20482		21.1	620	13.3	14.4	0.001	0.06	0.51	4.7	1.6	0.4	19.4	<0.01	0.05	3.4	0.007
CC20483		16.9	700	10.0	15.4	<0.001	0.07	0.39	3.7	1.5	0.4	23.3	<0.01	0.04	2.7	0.007
CC20484		16.3	380	9.9	12.1	0.001	0.03	0.37	3.4	1.3	0.3	12.8	<0.01	0.04	3.9	0.008
CC20485		17.8	610	7.4	12.4	0.001	0.05	0.30	2.8	1.5	0.3	16.4	<0.01	0.04	2.1	0.006
CC20486		24.6	880	11.2	8.8	0.002	0.09	0.56	3.6	2.1	0.3	31.6	<0.01	0.06	2.1	0.005
CC20487		17.6	530	10.3	12.5	0.001	0.05	0.39	3.8	1.5	0.4	20.3	<0.01	0.04	3.4	0.006
CC20488		35.4	1820	10.8	11.0	<0.001	0.03	2.36	4.6	1.7	0.4	75.3	<0.01	0.05	5.2	0.023
CC20489		40.7	1670	18.7	11.3	0.006	0.22	12.15	2.2	26.3	0.8	72.1	<0.01	0.18	1.3	<0.005
CC20490		7.8	830	15.7	10.6	0.014	0.18	11.80	1.2	16.6	0.6	44.2	<0.01	0.17	0.8	<0.005
CC20491		356.0	4030	14.4	10.7	0.004	0.26	41.20	9.8	30.4	1.1	172.0	0.02	0.44	3.0	<0.005
CC20492		73.5	490	13.7	7.3	0.001	0.18	12.40	2.5	15.4	0.8	118.0	<0.01	0.23	1.4	<0.005
CC20493		14.9	270	10.9	8.1	0.003	0.09	4.57	1.3	6.4	0.6	23.8	<0.01	0.14	0.7	<0.005
CC20494		87.4	360	9.3	7.4	0.022	0.16	7.74	1.8	11.1	0.5	61.4	<0.01	0.22	1.0	<0.005
CC29501		48.9	430	13.1	16.3	0.002	0.13	9.81	4.0	19.0	0.8	16.6	<0.01	0.17	3.5	0.021
CC29502		20.2	260	11.2	11.6	0.001	0.08	4.24	1.6	5.7	0.7	18.3	<0.01	0.10	2.3	0.018
CC29503		31.0	360	10.4	14.8	0.001	0.06	2.51	2.9	3.7	0.7	16.3	<0.01	0.07	3.0	0.019
CC29504		154.5	640	12.1	12.3	0.007	0.10	7.52	7.3	9.5	0.7	111.5	0.01	0.13	1.8	0.007
CC29505		13.2	620	1.5	1.7	0.004	0.15	1.19	0.7	2.9	<0.2	108.0	<0.01	<0.01	0.2	<0.005
CC29506		164.5	670	10.2	6.1	0.009	0.13	15.80	4.4	14.8	0.6	119.5	<0.01	0.16	1.5	0.005
CC29507		135.0	740	6.6	4.2	0.008	0.16	11.05	2.4	12.8	0.4	145.5	<0.01	0.09	0.7	<0.005
CC29508		137.5	800	6.6	6.3	0.008	0.14	8.44	2.6	9.6	0.4	117.5	<0.01	0.08	0.8	0.005
CC29509		52.8	730	1.7	2.0	0.002	0.17	2.81	0.7	5.3	<0.2	141.5	<0.01	0.02	0.3	<0.005
CC29510		159.5	820	5.0	4.4	0.018	0.19	8.23	2.2	14.7	0.3	147.0	<0.01	0.07	0.5	0.006
CC29511		86.8	1050	1.7	1.8	0.019	0.22	5.04	0.8	9.8	<0.2	136.0	<0.01	0.06	0.2	<0.005

Comments: Gold determinations by ME-MS41 are semi-quantitative due to the small sample weight used (0.5g).

ALS Chemex

EXCELLENCE IN ANALYTICAL CHEMISTRY

ALS Canada Ltd.

212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Finalized Date: 2-JUL-2007
Account: MTT

Project: NiMo

CERTIFICATE OF ANALYSIS VA07064995

Sample Description	Method	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	Zn-OG46
	Analyte	Tl	U	V	W	Y	Zn	Zr	Zn
	Units	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%
	LOR	0.02	0.05	1	0.05	0.05	2	0.5	0.01
CC20466		0.84	2.41	102	0.12	8.16	232	2.5	
CC20467		0.44	3.09	87	0.09	9.44	79	2.4	
CC20468		0.42	2.29	98	0.09	9.03	133	2.5	
CC20469		0.38	2.75	85	0.07	12.15	250	2.6	
CC20470		0.58	3.43	117	0.10	7.17	118	1.2	
CC20471		1.17	4.90	260	0.13	13.10	285	2.1	
CC20472		0.84	2.03	287	0.14	8.30	250	2.3	
CC20473		0.28	2.00	198	0.09	11.00	383	2.6	
CC20474		0.20	1.85	113	0.10	18.80	250	3.7	
CC20475		0.14	3.02	95	0.10	17.50	90	2.8	
CC20476		0.16	1.34	87	0.12	15.95	181	4.5	
CC20477		0.07	1.99	41	0.05	11.55	64	2.8	
CC20478		0.15	1.24	50	0.09	13.35	49	1.1	
CC20479		0.09	0.54	26	0.08	4.79	42	0.7	
CC20480		0.09	0.58	30	0.07	4.50	37	0.6	
CC20481		0.10	0.87	27	0.12	9.06	45	0.9	
CC20482		0.15	1.24	41	0.08	13.00	54	1.3	
CC20483		0.13	0.90	35	0.08	8.88	45	1.0	
CC20484		0.10	0.97	35	0.08	9.98	45	1.3	
CC20485		0.10	0.84	25	0.07	9.95	39	0.8	
CC20486		0.09	1.20	37	0.08	17.10	42	1.7	
CC20487		0.12	1.02	36	0.06	11.10	43	1.2	
CC20488		0.12	1.42	97	0.12	16.30	174	5.1	
CC20489		1.67	3.66	178	0.25	15.40	191	0.7	
CC20490		2.88	6.27	175	0.26	4.77	18	0.6	
CC20491		6.92	15.20	565	0.37	102.50	1420	8.2	
CC20492		3.26	3.32	292	0.28	16.95	201	3.0	
CC20493		2.07	3.37	142	0.16	6.08	33	<0.5	
CC20494		2.65	3.29	188	0.14	8.29	148	1.0	
CC29501		2.91	2.40	323	0.21	6.73	110	2.1	
CC29502		1.86	0.66	207	0.17	2.77	57	0.5	
CC29503		1.36	0.96	203	0.19	3.94	89	1.4	
CC29504		4.54	17.10	317	0.22	38.90	769	7.1	
CC29505		0.20	0.51	42	<0.05	1.73	104	1.3	
CC29506		1.43	6.14	584	0.25	27.50	950	6.9	
CC29507		0.94	6.01	415	0.14	22.50	791	5.3	
CC29508		0.96	6.60	336	0.14	23.10	914	4.6	
CC29509		0.17	1.13	79	0.05	4.50	324	2.3	
CC29510		0.75	5.24	158	0.10	21.00	605	5.1	
CC29511		0.22	1.82	63	<0.05	13.85	429	2.7	

Comments: Gold determinations by ME-MS41 are semi-quantitative due to the small sample weight used (0.5g).

ALS Chemex
EXCELLENCE IN ANALYTICAL CHEMISTRY
ALS Canada Ltd.
212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: STRATEGIC METALS LTD.
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NiMo

CERTIFICATE OF ANALYSIS VA07064995

Sample Description	Method	WEI-21	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41
	Analyte	Recvd Wt.	Ag	Al	As	Au	B	Ba	Be	Bi	Ca	Cd	Ce	Co	Cr	Cs
	Units	kg	ppm	%	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppm	ppm	ppm
	LOR	0.02	0.01	0.01	0.1	0.2	10	10	0.05	0.01	0.01	0.01	0.02	0.1	1	0.05
CC29512		0.06	0.05	0.09	1.5	<0.2	20	510	0.08	0.02	4.16	5.42	1.51	0.7	1	0.11
CC29513		0.18	1.10	1.07	28.7	<0.2	<10	990	0.84	0.15	2.40	10.90	17.35	4.5	24	0.83
CC29514		0.16	0.90	0.98	39.0	<0.2	<10	790	0.91	0.17	1.17	11.05	20.40	7.3	22	0.80
CC29515		0.14	0.26	1.00	37.8	<0.2	<10	440	0.62	0.21	0.09	1.51	17.20	10.6	20	0.83
CC29516		0.18	0.32	1.27	42.2	<0.2	<10	360	0.51	0.23	0.04	0.73	16.10	5.8	24	0.92
CC29517		0.20	0.31	1.68	31.4	<0.2	<10	400	0.59	0.20	0.06	0.44	24.50	7.7	31	1.00
CC29518		0.14	0.60	1.55	31.0	<0.2	<10	400	0.47	0.26	0.06	0.34	20.40	4.8	29	1.09
CC29519		0.20	0.61	1.24	85.2	<0.2	<10	1170	0.52	0.24	0.05	0.13	16.40	3.4	31	1.16
CC29520		0.18	0.66	0.99	24.0	<0.2	<10	1810	0.65	0.18	0.10	2.17	26.40	10.0	22	0.75
CC29521		0.18	1.11	2.06	25.6	<0.2	<10	350	0.50	0.25	0.05	0.41	23.10	7.0	38	1.32
CC29522		0.16	1.49	1.35	39.3	<0.2	<10	930	0.69	0.25	0.08	2.54	26.30	7.2	28	1.10
CC29523		0.22	0.43	0.45	12.4	<0.2	10	640	0.46	0.19	0.16	3.64	19.75	4.3	8	1.16
CC29524		0.24	0.66	1.23	16.9	<0.2	<10	1380	0.57	0.19	0.39	1.44	26.30	8.1	24	0.82
CC29525		0.16	1.17	0.58	19.1	<0.2	10	690	0.40	0.17	0.28	2.35	14.40	2.9	15	0.64
CC29526		0.24	0.64	0.83	24.0	<0.2	<10	500	0.59	0.18	0.27	2.83	19.65	3.1	17	0.68
CC29527		0.22	0.52	0.80	14.1	<0.2	10	570	0.59	0.18	0.29	2.14	18.60	5.5	16	0.69
CC29528		0.16	0.43	0.59	18.1	<0.2	10	570	0.63	0.16	0.50	2.54	11.75	3.1	11	0.55
CC29529		0.08	0.41	1.04	18.8	<0.2	10	3260	0.83	0.17	0.76	4.22	24.80	8.6	24	0.66
CC29533		0.08	0.89	1.56	14.4	<0.2	<10	780	0.67	0.23	0.71	3.08	23.30	14.2	30	1.21
CC29534		0.10	0.50	1.26	9.2	<0.2	<10	730	0.52	0.17	0.71	2.72	22.00	22.3	21	0.94
CC29535		0.16	0.37	1.16	9.3	<0.2	<10	500	0.49	0.18	0.22	0.96	30.30	6.3	23	0.72
CC29536		0.20	0.34	1.57	11.6	<0.2	<10	490	0.62	0.24	0.17	0.68	27.40	5.7	29	0.93
CC29537		0.12	0.61	1.17	8.9	<0.2	<10	380	0.45	0.16	0.45	0.50	19.75	3.3	21	1.12
CC29538		0.10	0.38	1.26	4.9	<0.2	<10	300	0.37	0.14	0.45	0.40	17.80	2.6	23	1.17
CC29539		0.12	0.46	1.86	11.2	<0.2	<10	510	1.01	0.22	0.17	1.25	31.10	9.9	31	1.18
CC29540		0.16	0.29	1.16	6.5	<0.2	<10	300	0.31	0.18	0.14	0.35	21.70	3.1	21	0.79
CC29541		0.14	0.30	1.32	6.3	<0.2	<10	330	0.43	0.20	0.16	0.39	24.80	3.7	24	0.90
CC29542		0.26	0.29	1.47	7.0	<0.2	<10	380	0.50	0.20	0.16	0.46	27.30	4.3	24	0.92
CC29543		0.10	0.84	0.97	4.9	<0.2	<10	530	0.40	0.12	0.47	2.41	20.20	2.7	17	0.91
CC29544		0.14	0.14	1.51	16.6	<0.2	<10	390	0.39	0.21	0.16	1.30	21.70	14.1	29	0.93
CC29545		0.26	0.28	1.67	15.7	<0.2	<10	740	0.62	0.21	0.45	1.25	24.20	7.2	29	1.01
CC29546		0.30	0.22	1.51	12.2	<0.2	<10	640	0.62	0.19	0.28	0.86	25.40	8.8	27	0.90
CC29547		0.12	0.39	1.25	9.6	<0.2	<10	580	0.56	0.16	0.62	2.38	22.70	7.5	24	0.69
CC29548		0.12	0.42	1.54	8.5	<0.2	<10	680	0.61	0.18	0.48	2.70	27.00	8.4	30	0.90
CC29549		0.04	0.44	1.27	9.9	<0.2	<10	670	0.42	0.17	0.84	5.51	17.85	7.8	28	0.82
CC29550		0.14	0.72	1.38	13.6	<0.2	<10	590	0.60	0.18	0.68	6.54	24.10	6.0	32	0.87
CC29551		0.14	0.94	1.37	14.1	<0.2	<10	700	0.61	0.18	0.61	8.06	24.50	8.9	42	0.88
CC29552		0.12	0.90	1.21	15.6	<0.2	<10	810	0.65	0.17	0.98	13.45	24.20	5.0	34	0.84
CC29553		0.24	0.96	1.33	16.7	<0.2	<10	760	0.74	0.19	0.79	8.48	28.90	7.7	36	0.85
CC29554		0.04	0.85	1.07	13.0	<0.2	<10	850	0.69	0.15	2.57	10.10	20.90	6.1	29	0.60

Comments: Gold determinations by ME-MS41 are semi-quantitative due to the small sample weight used (0.5g).

ALS Chemex

EXCELLENCE IN ANALYTICAL CHEMISTRY

ALS Canada Ltd.

212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: STRATEGIC METALS LTD.
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NiMo

Finalized Date: 2-JUL-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07064995

Sample Description	Method	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41
	Analyte	Cu	Fe	Ga	Ge	Hf	Hg	In	K	La	Li	Mg	Mn	Mo	Na	Nb
	Units	ppm	%	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	%	ppm	ppm	%	ppm
	LOR	0.2	0.01	0.05	0.05	0.02	0.01	0.005	0.01	0.2	0.1	0.01	5	0.05	0.01	0.05
CC29512		9.0	0.14	0.25	<0.05	0.02	0.11	<0.005	0.04	0.8	0.8	0.12	77	9.14	0.03	<0.05
CC29513		51.4	1.72	3.48	0.08	0.16	0.28	0.029	0.08	10.4	9.1	0.18	85	25.40	0.02	0.50
CC29514		64.9	2.37	3.14	0.08	0.15	0.28	0.035	0.10	11.4	7.9	0.13	117	47.00	0.02	0.42
CC29515		39.9	3.41	3.90	0.08	0.05	0.03	0.035	0.12	9.4	10.0	0.13	221	48.90	0.02	0.49
CC29516		41.3	3.96	4.89	0.09	0.02	0.04	0.039	0.12	8.7	13.0	0.20	117	51.30	0.02	0.67
CC29517		46.2	3.26	4.90	0.09	0.07	0.06	0.034	0.10	13.1	24.0	0.33	169	30.60	0.01	0.96
CC29518		28.2	3.43	6.34	0.10	0.02	0.04	0.033	0.11	11.0	16.0	0.23	148	42.80	0.01	1.01
CC29519		41.5	4.39	5.91	0.23	0.08	0.04	0.049	0.14	9.3	9.0	0.18	103	143.00	0.02	0.85
CC29520		41.0	2.31	3.28	0.08	0.07	0.07	0.033	0.10	14.3	9.0	0.21	286	31.60	0.02	0.47
CC29521		21.2	3.21	6.79	0.07	0.09	0.06	0.036	0.12	12.9	16.0	0.32	169	24.70	0.01	0.97
CC29522		51.1	3.03	4.88	0.10	0.05	0.18	0.042	0.14	14.3	9.0	0.19	137	62.00	0.02	0.56
CC29523		33.9	1.26	1.69	0.05	0.20	0.12	0.022	0.12	11.0	3.2	0.07	40	16.50	0.02	0.11
CC29524		28.2	2.04	4.14	0.06	0.04	0.12	0.028	0.10	14.0	11.0	0.30	173	22.20	0.02	0.59
CC29525		35.2	1.44	2.33	0.06	0.03	0.19	0.021	0.08	7.9	4.0	0.10	39	28.90	0.02	0.24
CC29526		32.6	2.42	2.84	0.10	0.05	0.18	0.028	0.07	10.5	6.9	0.15	58	52.90	0.01	0.45
CC29527		36.0	1.53	2.71	0.06	0.04	0.19	0.025	0.09	9.9	6.4	0.12	131	36.20	0.01	0.27
CC29528		30.5	1.32	2.06	0.05	0.04	0.15	0.022	0.09	6.5	3.3	0.07	59	34.90	0.01	0.14
CC29529		36.9	2.27	3.86	0.07	0.13	0.11	0.025	0.07	12.3	10.0	0.28	271	33.50	0.03	0.46
CC29533		51.1	2.13	6.05	0.05	0.04	0.11	0.028	0.08	12.3	11.0	0.25	480	24.60	0.02	0.62
CC29534		26.9	1.95	4.25	0.05	0.04	0.09	0.024	0.09	11.8	10.0	0.22	796	23.60	0.02	0.47
CC29535		26.0	1.62	3.98	0.05	0.06	0.08	0.025	0.07	15.7	11.0	0.25	128	13.40	0.01	0.64
CC29536		20.9	2.22	5.39	0.05	0.03	0.10	0.032	0.08	14.3	15.0	0.25	107	17.05	0.01	0.68
CC29537		15.2	1.63	4.45	0.05	0.02	0.10	0.022	0.06	10.2	10.7	0.17	41	13.25	0.01	0.56
CC29538		11.8	1.18	5.69	<0.05	<0.02	0.09	0.017	0.06	9.4	10.5	0.16	35	8.37	0.01	0.58
CC29539		27.8	2.90	6.14	0.06	0.04	0.05	0.033	0.12	15.8	11.6	0.23	325	18.40	0.02	0.65
CC29540		12.4	1.36	4.50	0.05	0.03	0.08	0.020	0.05	10.4	9.6	0.18	50	5.44	<0.01	0.45
CC29541		17.5	1.58	4.71	0.06	0.03	0.06	0.026	0.05	11.9	11.3	0.22	53	3.79	<0.01	0.52
CC29542		17.6	1.73	5.13	0.06	0.04	0.07	0.028	0.06	12.9	13.0	0.26	63	1.89	<0.01	0.53
CC29543		27.9	1.25	3.81	0.06	0.04	0.14	0.022	0.05	10.0	5.5	0.13	30	6.34	<0.01	0.36
CC29544		20.0	2.14	5.78	0.06	0.04	0.05	0.025	0.08	10.5	11.7	0.30	462	16.80	<0.01	0.56
CC29545		23.7	2.18	5.69	0.05	0.03	0.06	0.029	0.07	11.5	13.0	0.29	236	14.65	<0.01	0.49
CC29546		19.9	1.99	5.06	0.06	0.05	0.06	0.027	0.07	12.1	13.0	0.29	255	10.65	<0.01	0.51
CC29547		24.1	1.53	4.25	0.06	0.07	0.08	0.024	0.07	10.8	10.1	0.27	212	7.64	<0.01	0.44
CC29548		28.2	1.63	5.11	0.06	0.07	0.08	0.027	0.08	12.9	12.2	0.33	263	6.93	<0.01	0.51
CC29549		20.0	1.41	4.39	0.05	0.09	0.10	0.023	0.06	8.9	10.9	0.27	420	8.26	0.01	0.44
CC29550		38.7	1.62	4.76	0.08	0.08	0.14	0.027	0.06	11.9	11.0	0.27	155	4.53	<0.01	0.52
CC29551		40.2	1.67	4.72	0.08	0.06	0.22	0.030	0.08	12.7	11.3	0.30	241	7.24	<0.01	0.49
CC29552		48.8	1.30	4.32	0.08	0.08	0.25	0.025	0.08	12.7	10.1	0.27	99	3.43	<0.01	0.42
CC29553		46.0	1.62	4.70	0.08	0.10	0.22	0.029	0.10	14.5	11.9	0.35	136	7.09	<0.01	0.47
CC29554		42.6	1.34	3.53	0.07	0.13	0.19	0.023	0.07	11.3	8.7	0.73	157	5.23	0.01	0.38

Comments: Gold determinations by ME-MS41 are semi-quantitative due to the small sample weight used (0.5g).

ALS Chemex

EXCELLENCE IN ANALYTICAL CHEMISTRY

ALS Canada Ltd.

212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: STRATEGIC METALS LTD.
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NiMo

Finalized Date: 2-JUL-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07064995

Sample Description	Method	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41
	Analyte	Ni	P	Pb	Rb	Re	S	Sb	Sc	Se	Sn	Sr	Ta	Te	Th	Ti
	Units	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%
	LOR	0.2	10	0.2	0.1	0.001	0.01	0.05	0.1	0.2	0.2	0.2	0.01	0.01	0.2	0.005
CC29512		17.1	730	1.5	1.6	0.004	0.17	1.09	0.3	4.6	<0.2	148.0	<0.01	0.01	<0.2	<0.005
CC29513		106.5	630	10.2	10.0	0.014	0.10	8.29	4.9	9.6	0.6	108.0	<0.01	0.10	1.6	0.007
CC29514		152.5	430	12.1	9.7	0.011	0.11	8.11	5.7	10.1	0.6	67.6	<0.01	0.12	2.8	0.007
CC29515		79.7	410	14.0	12.7	0.003	0.15	6.92	3.6	11.3	0.6	26.7	<0.01	0.14	3.1	0.009
CC29516		51.4	550	14.1	13.6	0.002	0.16	7.88	3.4	14.4	0.7	24.6	<0.01	0.13	2.5	0.013
CC29517		38.4	400	11.2	12.6	0.001	0.09	6.93	4.0	12.5	0.6	17.2	<0.01	0.10	4.5	0.025
CC29518		22.9	610	14.3	14.9	0.001	0.11	7.39	3.1	15.7	0.8	19.4	<0.01	0.15	2.3	0.020
CC29519		14.9	1090	15.7	16.3	0.009	0.22	20.30	3.4	55.0	0.9	24.6	<0.01	0.36	3.4	0.019
CC29520		56.3	590	14.8	9.9	0.007	0.11	8.32	4.3	6.5	0.5	68.8	<0.01	0.12	4.1	0.015
CC29521		27.4	530	13.9	17.3	<0.001	0.11	9.40	4.3	6.3	0.8	25.6	<0.01	0.13	4.3	0.026
CC29522		87.4	780	17.7	15.1	0.005	0.17	12.70	4.4	12.5	0.8	88.2	<0.01	0.21	3.1	0.012
CC29523		64.9	210	11.7	11.6	0.056	0.07	3.50	3.2	3.2	0.5	55.0	<0.01	0.05	2.9	<0.005
CC29524		47.3	620	11.3	11.8	0.009	0.05	5.62	4.1	6.4	0.6	54.8	<0.01	0.10	3.0	0.017
CC29525		51.6	810	11.4	9.2	0.036	0.09	9.58	2.9	10.1	0.5	61.2	<0.01	0.12	1.0	0.005
CC29526		45.3	700	10.9	10.2	0.023	0.07	11.20	3.6	16.7	0.5	46.0	<0.01	0.12	2.5	0.009
CC29527		54.1	390	10.5	10.4	0.014	0.04	5.59	3.5	4.2	0.6	50.6	<0.01	0.12	2.2	0.006
CC29528		71.3	300	9.3	9.0	0.012	0.06	4.54	2.7	4.8	0.5	60.0	<0.01	0.13	1.3	<0.005
CC29529		65.5	760	11.9	11.5	0.008	0.10	5.24	4.1	4.4	0.6	99.4	<0.01	0.07	2.6	0.009
CC29533		45.7	1170	14.3	12.1	0.005	0.09	3.83	3.0	3.5	0.7	56.1	<0.01	0.08	0.9	0.010
CC29534		44.6	680	9.2	17.2	0.009	0.06	2.45	3.6	3.7	0.5	50.1	<0.01	0.05	1.8	0.009
CC29535		26.5	400	9.3	10.3	0.002	0.03	3.64	3.8	2.4	0.5	26.6	<0.01	0.07	4.2	0.019
CC29536		25.3	510	12.8	14.9	0.006	0.03	3.80	4.1	3.8	0.7	26.4	<0.01	0.08	2.8	0.012
CC29537		16.6	770	9.4	11.7	0.020	0.08	3.59	2.8	4.8	0.5	31.6	<0.01	0.06	1.2	0.009
CC29538		13.0	730	8.6	9.2	0.011	0.07	2.22	2.6	3.0	0.6	31.4	<0.01	0.04	1.1	0.009
CC29539		33.6	1580	14.7	19.9	0.004	0.04	2.99	3.5	2.6	0.7	18.8	<0.01	0.06	1.4	0.013
CC29540		13.2	450	9.9	11.7	0.005	0.04	2.12	2.5	2.3	0.5	16.1	0.01	0.06	2.1	0.010
CC29541		15.8	490	11.7	12.5	0.005	0.03	2.40	3.1	2.5	0.5	17.6	0.01	0.07	2.7	0.011
CC29542		17.3	420	11.9	12.8	0.004	0.02	2.27	3.7	2.1	0.6	18.4	0.01	0.07	3.4	0.011
CC29543		29.9	710	7.9	10.4	0.004	0.09	2.32	3.3	3.3	0.4	48.4	0.01	0.07	1.5	0.008
CC29544		33.8	430	11.9	14.2	0.001	0.03	3.71	3.1	1.9	0.7	31.7	<0.01	0.08	2.8	0.012
CC29545		33.8	360	12.3	13.4	0.004	0.02	3.46	3.6	2.1	0.7	36.1	<0.01	0.08	2.4	0.010
CC29546		34.1	360	11.0	13.1	0.003	0.02	3.07	3.7	1.8	0.6	26.3	<0.01	0.06	3.3	0.011
CC29547		39.2	520	10.0	10.2	0.004	0.04	3.28	3.4	2.6	0.5	45.4	<0.01	0.06	2.4	0.009
CC29548		47.1	460	9.9	13.3	0.003	0.03	3.45	4.3	2.3	0.6	36.9	<0.01	0.05	3.2	0.012
CC29549		44.1	520	9.8	11.3	0.006	0.05	4.56	3.5	3.6	0.5	55.3	<0.01	0.06	2.5	0.010
CC29550		58.0	470	11.6	12.1	0.008	0.05	7.60	4.2	5.7	0.5	53.4	<0.01	0.08	3.0	0.010
CC29551		79.1	450	10.3	13.9	0.005	0.03	9.31	4.5	3.5	0.6	48.6	<0.01	0.08	3.3	0.011
CC29552		80.4	710	11.9	13.2	0.009	0.06	7.98	4.0	5.7	0.5	68.7	<0.01	0.08	2.6	0.008
CC29553		86.9	690	11.3	14.6	0.003	0.03	7.67	4.9	2.8	0.6	50.9	<0.01	0.09	3.7	0.013
CC29554		78.0	710	9.1	9.3	0.003	0.08	6.21	3.4	5.9	0.4	81.7	<0.01	0.07	2.0	0.009

Comments: Gold determinations by ME-MS41 are semi-quantitative due to the small sample weight used (0.5g).

ALS Chemex

EXCELLENCE IN ANALYTICAL CHEMISTRY

ALS Canada Ltd.

212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Finalized Date: 2-JUL-2007
Account: MTT

Project: NiMo

CERTIFICATE OF ANALYSIS VA07064995

Sample Description	Method	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	Zn-OG46
	Analyte	Tl	U	V	W	Y	Zn	Zr	Zn
	Units	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%
	LOR	0.02	0.05	1	0.05	0.05	2	0.5	0.01
CC29512		0.04	0.20	32	<0.05	0.92	225	0.8	
CC29513		1.77	5.89	270	0.16	21.30	587	5.5	
CC29514		2.49	4.34	273	0.20	22.60	807	5.8	
CC29515		2.46	1.86	253	0.17	7.87	218	2.5	
CC29516		2.20	1.76	242	0.20	5.26	140	1.0	
CC29517		1.44	1.61	186	0.20	6.05	84	3.0	
CC29518		1.73	1.35	272	0.29	4.16	77	0.8	
CC29519		3.90	3.56	582	0.31	5.78	51	4.4	
CC29520		2.72	3.67	170	0.18	15.05	175	2.8	
CC29521		1.78	1.43	270	0.21	4.33	79	3.9	
CC29522		5.07	4.79	282	0.26	14.25	218	2.2	
CC29523		1.91	4.18	88	0.09	19.10	242	7.3	
CC29524		1.21	2.82	153	0.28	10.80	157	1.4	
CC29525		1.75	4.81	149	0.17	10.10	123	1.1	
CC29526		1.77	4.84	209	0.19	12.80	115	1.9	
CC29527		1.73	6.08	200	0.16	14.45	153	1.6	
CC29528		1.88	4.90	173	0.15	12.15	187	1.4	
CC29529		0.45	9.98	277	0.17	17.50	292	3.5	
CC29533		0.87	2.47	206	0.17	10.90	188	0.8	
CC29534		0.86	2.39	162	0.17	11.20	181	1.1	
CC29535		0.80	2.93	126	0.15	9.05	105	2.3	
CC29536		0.82	2.93	155	0.14	7.88	86	1.0	
CC29537		0.63	2.35	98	0.11	5.45	46	0.8	
CC29538		0.70	1.68	83	0.13	3.60	45	0.7	
CC29539		0.63	2.68	136	0.13	8.27	86	0.9	
CC29540		0.37	1.14	74	0.13	4.02	54	0.7	
CC29541		0.39	1.42	85	0.18	5.08	63	0.7	
CC29542		0.40	1.42	81	0.12	5.88	74	1.0	
CC29543		0.75	1.63	74	0.09	9.27	111	1.0	
CC29544		0.96	1.21	179	0.18	4.43	226	1.1	
CC29545		0.75	1.43	200	0.15	6.90	222	0.7	
CC29546		0.63	1.40	159	0.16	7.48	240	1.4	
CC29547		0.44	1.69	129	0.11	9.72	257	1.8	
CC29548		0.56	2.28	163	0.14	11.20	364	1.9	
CC29549		0.57	1.98	205	0.11	6.47	546	2.3	
CC29550		0.66	3.69	252	0.13	12.15	768	2.4	
CC29551		0.86	3.39	421	0.14	12.35	1310	2.3	
CC29552		0.81	4.74	414	0.17	16.60	1130	2.6	
CC29553		0.88	2.53	396	0.16	17.15	974	3.4	
CC29554		0.50	2.49	293	0.13	16.65	762	4.0	

Comments: Gold determinations by ME-MS41 are semi-quantitative due to the small sample weight used (0.5g).

ALS Chemex

EXCELLENCE IN ANALYTICAL CHEMISTRY

ALS Canada Ltd.

212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: STRATEGIC METALS LTD.
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NiMo

Finalized Date: 2-JUL-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07064995

Sample Description	Method	WEI-21	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41
	Analyte	Recvd Wt.	Ag	Al	As	Au	B	Ba	Be	Bi	Ca	Cd	Ce	Co	Cr	Cs
	Units	kg	ppm	%	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppm	ppm	ppm
	LOR	0.02	0.01	0.01	0.1	0.2	10	10	0.05	0.01	0.01	0.01	0.02	0.1	1	0.05
CC29555		0.16	0.40	1.12	6.3	<0.2	<10	1510	0.48	0.18	0.22	0.58	27.30	7.5	18	0.63
CC29556		0.20	0.44	1.18	3.8	<0.2	<10	1260	0.62	0.20	0.35	0.74	30.00	3.7	21	0.60
CC29557		0.08	0.52	1.09	11.7	<0.2	<10	1540	0.50	0.14	1.91	3.96	25.20	65.6	20	0.64
CC29558		0.14	1.37	1.22	24.4	<0.2	<10	760	0.69	0.18	0.92	11.30	24.20	8.5	42	0.88
CC29559		0.32	3.77	1.40	7.9	<0.2	<10	560	0.82	0.19	0.77	51.00	28.00	8.1	58	0.84
CC29560		0.12	0.21	1.11	13.8	<0.2	<10	590	0.59	0.15	0.16	0.91	22.90	6.5	20	0.70
CC29561		0.26	0.27	1.17	17.8	<0.2	<10	710	0.73	0.18	0.23	2.68	25.20	5.8	19	0.79
CC29562		0.18	0.30	1.11	14.8	<0.2	<10	670	0.62	0.16	0.16	1.36	20.80	4.1	19	0.78
CC29563		0.20	0.36	1.39	20.9	<0.2	<10	400	0.45	0.21	0.43	1.75	23.90	4.9	27	0.91
CC29564		0.18	0.48	1.47	16.3	<0.2	<10	380	0.55	0.21	0.22	1.28	28.80	4.3	29	0.78
CC29568		0.18	0.39	1.29	74.5	<0.2	<10	580	0.76	0.23	0.04	1.21	13.85	3.5	26	0.92
CC29569		0.12	0.28	0.88	68.2	<0.2	<10	410	0.28	0.24	0.02	0.49	11.65	2.3	22	0.59
CC29570		0.14	0.31	0.43	14.9	<0.2	<10	370	0.49	0.14	0.54	2.03	10.95	4.2	8	0.44
CC29571		0.16	0.36	0.44	15.1	<0.2	<10	340	0.57	0.14	0.37	4.28	12.55	5.6	8	0.41
CC29572		0.02	0.79	0.44	18.6	<0.2	10	480	0.43	0.07	2.85	13.25	8.38	7.0	19	0.47
CC29573		0.04	0.61	1.01	10.4	<0.2	<10	2400	0.39	0.15	0.85	1.58	19.80	18.8	17	0.67
CC29574		0.20	0.20	1.01	13.0	<0.2	<10	830	0.63	0.16	0.18	0.84	25.00	4.8	17	0.62
CC29575		0.10	0.27	0.68	15.0	<0.2	<10	270	0.23	0.15	0.03	0.63	19.40	3.1	11	0.66
CC29576		0.12	0.47	2.06	14.0	<0.2	<10	1490	0.82	0.21	0.23	5.09	34.30	7.8	27	1.15
CC29577		0.12	0.31	1.36	14.4	<0.2	<10	320	0.34	0.20	0.17	2.08	19.60	6.3	23	0.86
CC29578		0.12	0.89	1.45	10.9	<0.2	<10	490	0.53	0.17	0.13	1.69	23.40	3.6	24	0.99
CC29579		0.08	1.62	1.90	13.1	<0.2	<10	760	0.68	0.24	0.21	1.59	28.00	5.5	30	1.38
CC29580		0.12	0.28	1.15	10.3	<0.2	<10	280	0.33	0.18	0.07	0.72	20.80	2.8	21	0.94
CC29581		0.12	0.31	0.95	9.3	<0.2	<10	640	0.55	0.14	1.90	2.01	20.70	7.9	15	0.53
CC29582		0.14	0.27	1.36	7.2	<0.2	<10	490	0.44	0.17	0.71	0.50	22.60	4.7	20	0.85
CC29583		0.12	0.25	1.51	9.1	<0.2	<10	600	0.57	0.18	0.23	0.36	29.50	6.7	23	0.86
CC29584		0.24	0.36	1.56	11.8	<0.2	<10	790	0.68	0.19	0.55	0.75	28.30	8.1	26	0.77
CC29585		0.14	0.96	1.03	29.1	<0.2	<10	390	0.27	0.23	0.04	0.26	25.40	3.3	24	0.96
CC29586		0.08	1.64	0.64	21.5	<0.2	<10	300	0.16	0.28	0.03	0.22	20.10	1.2	17	1.03
CC29587		0.12	0.61	1.28	30.3	<0.2	<10	340	0.24	0.24	0.06	0.37	19.00	4.1	31	0.99
CC29588		0.12	1.23	1.82	31.0	<0.2	<10	260	0.31	0.27	0.04	0.26	20.60	5.4	38	1.33
CC29589		0.14	0.49	2.14	22.3	<0.2	<10	170	0.48	0.23	0.04	0.32	20.40	6.5	33	1.16
CC29590		0.10	0.19	1.70	28.2	<0.2	<10	190	0.31	0.29	0.04	0.21	20.20	6.0	32	1.24
CC29591		0.12	0.09	0.57	28.9	<0.2	<10	120	0.12	0.27	0.02	0.12	26.20	2.3	14	1.10
CC29592		0.12	0.16	0.71	17.9	<0.2	<10	150	0.15	0.19	0.01	0.66	19.25	2.7	13	0.99
CC29593		0.16	0.15	1.31	20.0	<0.2	<10	420	0.41	0.18	0.06	3.64	22.10	5.9	22	1.10
CC29594		0.20	1.86	0.95	41.3	<0.2	<10	1150	0.70	0.20	0.66	22.90	29.50	5.9	36	0.99
CC29595		0.10	0.61	0.72	8.3	<0.2	<10	3070	0.46	0.15	0.50	1.14	14.55	16.1	15	0.43
CC29596		0.10	0.23	1.37	21.6	<0.2	<10	1700	0.64	0.18	0.43	1.42	26.00	9.4	21	0.72
CC29597		0.08	0.18	1.40	11.9	<0.2	<10	1050	0.54	0.16	0.39	0.85	25.90	5.9	23	0.78

Comments: Gold determinations by ME-MS41 are semi-quantitative due to the small sample weight used (0.5g).

ALS Chemex

EXCELLENCE IN ANALYTICAL CHEMISTRY

ALS Canada Ltd.

212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: STRATEGIC METALS LTD.
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NiMo

Finalized Date: 2-JUL-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07064995

Sample Description	Method	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41
	Analyte	Cu	Fe	Ga	Ge	Hf	Hg	In	K	La	Li	Mg	Mn	Mo	Na	Nb
	Units	ppm	%	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	%	ppm	ppm	%	ppm
	LOR	0.2	0.01	0.05	0.05	0.02	0.01	0.005	0.01	0.2	0.1	0.01	5	0.05	0.01	0.05
CC29555		25.7	2.03	3.49	0.07	0.04	0.10	0.025	0.07	12.3	9.0	0.22	126	2.56	<0.01	0.36
CC29556		33.9	1.18	3.69	0.06	0.04	0.13	0.030	0.06	13.4	9.8	0.23	51	1.02	<0.01	0.37
CC29557		17.9	4.38	3.01	0.07	0.09	0.13	0.024	0.05	8.1	6.7	0.20	5680	39.50	<0.01	0.29
CC29558		58.7	1.85	4.44	0.09	0.11	0.33	0.026	0.08	12.5	9.7	0.30	268	12.85	<0.01	0.49
CC29559		147.5	1.31	5.34	0.13	0.15	0.78	0.032	0.10	16.5	11.2	0.33	124	3.23	0.01	0.64
CC29560		27.0	1.95	3.56	0.05	0.04	0.08	0.024	0.07	10.6	8.1	0.20	101	18.10	<0.01	0.38
CC29561		31.5	2.31	3.71	0.07	0.04	0.11	0.027	0.07	11.7	7.2	0.18	129	18.65	<0.01	0.40
CC29562		26.6	1.90	3.44	0.06	0.03	0.11	0.025	0.07	9.8	6.7	0.16	78	17.35	<0.01	0.34
CC29563		25.6	1.96	4.84	0.07	0.03	0.12	0.029	0.07	11.0	10.5	0.26	131	17.45	<0.01	0.59
CC29564		36.3	1.95	5.03	0.09	0.04	0.13	0.032	0.07	13.3	10.7	0.26	107	17.25	<0.01	0.64
CC29568		91.9	3.36	4.26	0.22	0.04	0.05	0.051	0.22	7.0	3.8	0.07	69	70.80	0.01	0.27
CC29569		52.4	3.60	4.79	0.18	0.04	0.04	0.036	0.16	6.0	1.9	0.05	41	76.70	0.01	0.39
CC29570		30.7	1.48	1.45	0.06	0.03	0.12	0.023	0.07	5.5	0.9	0.03	48	34.50	<0.01	0.08
CC29571		37.1	1.39	1.44	0.06	0.04	0.13	0.022	0.07	6.5	0.9	0.03	92	33.10	<0.01	0.08
CC29572		42.7	0.82	1.44	0.08	0.09	0.16	0.012	0.04	4.3	1.2	0.11	949	24.20	0.01	0.12
CC29573		19.4	3.69	2.92	0.06	0.08	0.14	0.021	0.06	9.2	6.5	0.20	1890	25.70	<0.01	0.25
CC29574		25.0	2.13	3.27	0.07	0.04	0.09	0.023	0.07	11.8	5.8	0.18	75	17.05	<0.01	0.34
CC29575		17.4	1.60	3.66	0.05	<0.02	0.04	0.018	0.07	9.4	2.0	0.07	81	24.50	<0.01	0.39
CC29576		32.8	2.04	5.92	0.09	0.06	0.19	0.033	0.10	15.0	12.2	0.28	116	13.80	<0.01	0.56
CC29577		15.4	1.84	5.28	0.06	<0.02	0.08	0.019	0.08	9.7	9.4	0.27	192	17.80	0.01	0.52
CC29578		37.3	1.77	5.10	0.06	0.03	0.12	0.028	0.06	11.0	9.2	0.20	52	5.38	<0.01	0.49
CC29579		56.4	2.01	6.28	0.08	0.04	0.20	0.038	0.09	12.7	10.8	0.22	86	9.64	<0.01	0.58
CC29580		19.6	1.49	4.71	0.05	0.02	0.09	0.022	0.06	9.9	6.7	0.16	54	10.50	<0.01	0.57
CC29581		25.2	1.69	2.83	0.06	0.08	0.12	0.021	0.06	10.0	8.0	0.25	313	7.52	0.01	0.38
CC29582		16.6	1.71	4.62	0.05	0.02	0.07	0.021	0.06	10.7	10.7	0.27	90	2.65	0.01	0.54
CC29583		20.4	2.41	4.99	0.06	0.03	0.07	0.025	0.06	13.3	11.9	0.28	159	5.74	<0.01	0.58
CC29584		28.9	2.21	4.88	0.07	0.07	0.10	0.028	0.07	12.9	12.2	0.31	169	9.39	<0.01	0.57
CC29585		19.5	2.40	5.41	0.09	0.03	0.12	0.033	0.09	12.7	6.5	0.20	85	59.90	<0.01	0.55
CC29586		16.3	1.51	7.12	0.06	<0.02	0.06	0.019	0.07	9.8	0.9	0.03	25	60.70	<0.01	0.35
CC29587		22.8	3.65	6.92	0.10	0.02	0.06	0.042	0.12	10.0	9.7	0.18	145	48.80	<0.01	0.89
CC29588		34.6	4.05	8.28	0.08	0.05	0.11	0.049	0.09	10.3	14.3	0.26	227	41.50	<0.01	1.05
CC29589		32.6	3.38	6.71	0.07	0.08	0.07	0.041	0.06	10.1	17.8	0.26	173	26.60	<0.01	1.07
CC29590		30.9	5.21	9.47	0.09	0.03	0.05	0.045	0.08	9.7	14.8	0.26	249	39.10	0.01	1.48
CC29591		16.9	1.48	7.55	0.05	<0.02	0.03	0.013	0.05	12.2	1.3	0.04	77	38.60	<0.01	0.74
CC29592		16.7	1.56	6.05	<0.05	<0.02	0.03	0.014	0.05	9.6	1.4	0.05	52	30.00	<0.01	0.45
CC29593		23.2	2.37	4.47	0.06	0.04	0.12	0.026	0.09	11.0	10.6	0.25	165	15.60	<0.01	0.62
CC29594		93.5	1.86	3.45	0.10	0.09	0.74	0.033	0.12	15.1	6.5	0.20	100	46.20	<0.01	0.30
CC29595		28.3	2.36	2.01	0.05	0.05	0.17	0.026	0.07	6.6	3.0	0.14	571	5.59	<0.01	0.20
CC29596		25.0	2.31	4.19	0.08	0.05	0.09	0.026	0.06	11.7	8.5	0.24	192	16.55	<0.01	0.42
CC29597		17.2	2.10	4.54	0.06	0.04	0.07	0.024	0.07	12.0	10.6	0.32	140	4.35	<0.01	0.46

Comments: Gold determinations by ME-MS41 are semi-quantitative due to the small sample weight used (0.5g).

ALS Chemex
EXCELLENCE IN ANALYTICAL CHEMISTRY
ALS Canada Ltd.
212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: STRATEGIC METALS LTD.
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NiMo

CERTIFICATE OF ANALYSIS VA07064995

Sample Description	Method	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41
	Analyte	Ni	P	Pb	Rb	Re	S	Sb	Sc	Se	Sn	Sr	Ta	Te	Th	Ti
	Units	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%
	LOR	0.2	10	0.2	0.1	0.001	0.01	0.05	0.1	0.2	0.2	0.2	0.01	0.01	0.2	0.005
CC29555		22.3	610	11.0	11.1	0.001	0.04	1.00	3.3	1.8	0.3	24.4	<0.01	0.04	2.7	0.008
CC29556		20.3	430	13.1	10.7	0.003	0.04	0.97	3.6	2.1	0.4	27.6	<0.01	0.05	3.1	0.007
CC29557		38.8	1170	7.3	8.4	0.014	0.13	2.45	2.9	4.3	0.3	116.5	<0.01	0.06	1.4	0.006
CC29558		108.0	530	11.4	13.2	0.011	0.06	10.80	4.9	6.9	0.5	60.6	<0.01	0.10	3.3	0.013
CC29559		359.0	450	10.3	12.9	0.006	0.06	19.45	7.4	10.0	0.6	69.7	<0.01	0.09	3.8	0.016
CC29560		43.4	280	9.9	11.3	0.004	0.03	2.61	3.6	3.2	0.5	20.2	<0.01	0.05	3.0	0.009
CC29561		61.3	470	11.6	13.2	0.004	0.04	2.77	4.1	5.8	0.5	23.2	<0.01	0.06	3.0	0.007
CC29562		53.2	340	11.0	12.1	0.006	0.04	2.70	3.6	5.1	0.5	20.9	<0.01	0.06	2.4	0.007
CC29563		36.9	560	11.4	13.1	0.010	0.06	5.04	3.6	6.9	0.6	41.2	<0.01	0.12	2.5	0.012
CC29564		33.0	540	12.0	11.6	0.007	0.04	11.15	4.4	9.3	0.6	32.1	<0.01	0.08	3.0	0.015
CC29568		93.8	830	15.1	20.6	0.007	0.61	6.54	3.4	51.4	0.8	56.4	<0.01	0.31	2.1	0.006
CC29569		65.9	460	14.7	16.1	0.002	0.40	6.06	2.2	39.8	0.8	56.8	<0.01	0.38	2.2	0.008
CC29570		82.0	270	8.7	7.8	0.007	0.08	3.08	2.5	5.6	0.4	55.5	<0.01	0.07	1.3	<0.005
CC29571		89.3	250	8.3	7.2	0.006	0.04	3.30	3.1	3.6	0.4	42.8	<0.01	0.07	1.4	<0.005
CC29572		176.0	980	4.1	6.1	0.021	0.22	7.39	1.6	12.2	0.2	160.0	<0.01	0.07	0.4	<0.005
CC29573		46.8	720	8.7	9.9	0.030	0.11	1.88	3.0	3.2	0.3	58.2	<0.01	0.05	1.9	0.006
CC29574		32.0	300	11.0	10.5	0.006	0.02	1.87	3.5	4.9	0.4	20.4	<0.01	0.06	3.3	0.006
CC29575		26.4	410	7.9	8.9	0.001	0.07	2.72	1.1	2.5	0.5	12.2	<0.01	0.07	0.4	0.013
CC29576		81.1	550	11.9	16.1	0.005	0.04	2.38	5.2	4.3	0.7	37.1	<0.01	0.10	2.8	0.008
CC29577		24.4	450	11.5	12.8	0.002	0.03	4.65	2.4	3.2	0.6	28.3	<0.01	0.08	1.6	0.012
CC29578		23.4	730	10.9	12.5	0.003	0.03	3.11	2.7	3.9	0.6	26.3	<0.01	0.07	1.4	0.009
CC29579		26.6	1010	13.8	15.1	0.004	0.07	3.72	4.1	4.5	0.7	31.5	<0.01	0.10	1.4	0.009
CC29580		14.9	410	9.8	11.6	0.002	0.03	2.96	2.2	2.9	0.5	15.9	<0.01	0.07	1.5	0.012
CC29581		40.3	760	9.2	7.6	0.003	0.09	1.83	2.7	2.8	0.3	68.1	<0.01	0.05	1.5	0.008
CC29582		17.5	610	10.2	11.1	0.001	0.05	1.00	2.7	1.8	0.5	34.1	<0.01	0.05	1.6	0.012
CC29583		23.9	490	11.4	11.7	0.002	0.03	1.53	3.8	2.0	0.5	21.9	<0.01	0.05	3.0	0.012
CC29584		27.7	510	12.7	10.8	0.005	0.04	3.60	4.2	3.7	0.5	30.9	<0.01	0.06	3.7	0.010
CC29585		15.6	510	14.7	13.2	<0.001	0.12	19.85	2.7	8.7	0.8	27.2	<0.01	0.18	3.1	0.016
CC29586		5.5	430	17.3	7.5	0.001	0.11	13.25	1.1	6.3	1.2	19.9	<0.01	0.22	0.7	0.013
CC29587		12.7	630	13.7	13.3	<0.001	0.25	13.70	2.6	12.8	0.9	24.6	<0.01	0.17	1.9	0.026
CC29588		14.6	450	13.7	12.6	<0.001	0.10	25.60	3.4	9.0	0.9	17.5	<0.01	0.16	3.0	0.023
CC29589		19.7	310	11.8	12.0	<0.001	0.05	7.63	3.3	4.5	0.8	11.1	0.01	0.11	3.6	0.026
CC29590		15.9	440	13.5	13.3	<0.001	0.07	9.78	2.9	9.1	0.9	14.8	<0.01	0.14	2.7	0.042
CC29591		9.9	240	11.9	8.2	<0.001	0.04	4.86	1.2	2.6	1.0	20.0	<0.01	0.13	1.4	0.034
CC29592		29.7	270	8.4	7.8	<0.001	0.04	2.32	1.4	3.0	0.9	13.8	<0.01	0.09	1.1	0.015
CC29593		62.9	290	10.2	11.9	<0.001	0.08	2.83	3.3	2.4	0.5	19.6	<0.01	0.06	2.8	0.014
CC29594		175.5	750	9.8	12.2	0.003	0.05	19.10	5.8	6.2	0.7	56.4	<0.01	0.15	3.3	0.011
CC29595		28.8	750	8.1	7.5	0.002	0.07	1.35	3.4	2.2	0.3	46.5	<0.01	0.05	1.8	0.005
CC29596		47.6	480	11.0	11.5	0.011	0.04	2.30	3.7	7.4	0.5	50.1	<0.01	0.14	2.7	0.007
CC29597		27.5	550	10.5	10.8	0.002	0.04	1.30	3.2	2.2	0.5	31.3	<0.01	0.06	2.7	0.010

Comments: Gold determinations by ME-MS41 are semi-quantitative due to the small sample weight used (0.5g).

ALS Chemex

EXCELLENCE IN ANALYTICAL CHEMISTRY

ALS Canada Ltd.

212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NiMo

Finalized Date: 2-JUL-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07064995

Sample Description	Method	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	Zn-OG46
	Analyte	Tl	U	V	W	Y	Zn	Zr	Zn
	Units	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%
	LOR	0.02	0.05	1	0.05	0.05	2	0.5	0.01
CC29555		0.13	1.20	51	0.12	9.79	89	0.9	
CC29556		0.14	1.25	47	0.07	11.10	85	1.0	
CC29557		0.22	1.53	98	0.09	10.95	435	2.3	
CC29558		1.11	5.28	498	0.13	17.70	1400	4.0	
CC29559		2.80	18.75	550	0.15	31.50	4540	7.8	
CC29560		0.79	2.26	129	0.12	10.25	161	1.4	
CC29561		0.96	3.80	116	0.13	15.45	194	1.4	
CC29562		1.40	3.48	124	0.11	11.85	159	1.0	
CC29563		1.89	5.12	160	0.14	7.61	122	1.2	
CC29564		1.27	11.30	227	0.19	11.30	96	1.5	
CC29568		9.30	3.39	322	0.19	8.14	208	1.4	
CC29569		7.75	1.85	356	0.23	4.37	143	2.0	
CC29570		1.35	2.87	111	0.13	15.10	174	1.2	
CC29571		1.21	5.40	116	0.12	20.80	304	1.1	
CC29572		0.81	3.01	220	0.07	15.90	935	3.2	
CC29573		0.16	1.45	72	0.07	11.00	414	1.9	
CC29574		0.69	2.57	107	0.14	13.90	148	1.7	
CC29575		0.88	0.78	109	0.16	3.89	79	<0.5	
CC29576		1.44	3.06	126	0.15	23.20	148	1.5	
CC29577		0.66	1.37	168	0.19	4.25	108	<0.5	
CC29578		0.49	2.55	97	0.12	7.50	59	0.5	
CC29579		0.66	4.09	102	0.19	12.55	76	0.9	
CC29580		0.45	1.62	93	0.15	4.22	47	<0.5	
CC29581		0.32	1.86	58	0.16	11.25	128	2.4	
CC29582		0.21	1.21	61	0.12	5.82	68	0.6	
CC29583		0.25	1.59	77	0.27	9.39	72	1.0	
CC29584		0.29	2.67	103	0.20	10.35	115	2.2	
CC29585		3.22	2.39	370	0.24	3.98	62	1.3	
CC29586		2.29	2.07	309	0.33	2.71	18	<0.5	
CC29587		2.91	1.72	203	0.31	2.70	49	0.5	
CC29588		1.45	1.91	285	0.28	2.62	49	2.1	
CC29589		0.96	1.25	173	0.23	2.79	59	3.0	
CC29590		1.62	1.29	231	0.26	2.86	60	1.1	
CC29591		0.93	0.87	239	0.23	2.35	35	<0.5	
CC29592		0.83	0.65	173	0.20	2.29	74	<0.5	
CC29593		1.71	1.30	159	0.14	7.12	567	1.4	
CC29594		1.72	5.21	476	0.19	27.30	1510	3.3	
CC29595		0.12	1.41	41	0.07	11.35	93	1.4	
CC29596		1.26	6.21	120	0.13	12.65	162	1.4	
CC29597		0.37	1.81	99	0.11	7.99	154	1.1	

Comments: Gold determinations by ME-MS41 are semi-quantitative due to the small sample weight used (0.5g).

ALS Chemex

EXCELLENCE IN ANALYTICAL CHEMISTRY

ALS Canada Ltd.

212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NiMo

Finalized Date: 2-JUL-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07064995

Sample Description	Method	WEI-21	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41
	Analyte	Recvd Wt.	Ag	Al	As	Au	B	Ba	Be	Bi	Ca	Cd	Ce	Co	Cr	Cs
	Units	kg	ppm	%	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppm	ppm	ppm
	LOR	0.02	0.01	0.01	0.1	0.2	10	10	0.05	0.01	0.01	0.01	0.02	0.1	1	0.05
CC29598		0.08	0.23	1.24	8.8	<0.2	<10	670	0.40	0.16	0.18	0.48	21.80	4.5	22	0.75
CC29599		0.10	0.26	1.23	8.5	<0.2	<10	710	0.42	0.16	0.23	0.50	22.10	4.1	21	0.78
CC29600		0.16	0.12	0.40	13.8	<0.2	<10	290	0.38	0.13	0.13	1.32	10.90	5.5	7	0.51
CC29601		0.30	0.61	1.63	5.6	<0.2	10	550	0.93	0.13	2.28	1.76	42.40	7.7	27	0.94
CC29603		0.18	0.50	1.41	7.2	<0.2	10	570	0.78	0.11	2.34	1.69	38.60	6.2	23	0.84
CC29604		0.14	0.61	1.33	8.3	<0.2	10	600	0.82	0.11	2.94	1.84	36.00	6.0	23	0.83
CC29605		0.16	0.50	1.58	10.0	<0.2	10	590	0.93	0.13	2.91	1.41	39.90	7.7	27	0.80
CC29606		0.22	0.50	1.49	5.0	<0.2	10	570	0.81	0.12	3.79	1.62	36.90	6.8	26	0.80
CC29607		0.12	0.47	1.37	9.8	<0.2	<10	660	0.81	0.11	1.30	1.38	36.90	7.9	24	0.76
CC29608		0.24	0.58	1.57	10.0	<0.2	<10	540	0.99	0.13	1.83	1.34	36.10	6.3	26	0.82
CC29609		0.14	0.69	1.46	12.9	<0.2	10	470	0.78	0.14	3.92	2.01	34.00	7.9	25	0.92
CC29610		0.12	0.25	1.64	9.8	<0.2	<10	1030	0.74	0.21	0.51	0.78	36.80	8.0	26	0.77
CC29611		0.20	0.26	1.63	10.2	<0.2	<10	1110	0.69	0.20	0.52	0.82	36.00	8.5	27	0.89
CC29612		0.20	0.23	1.49	10.4	<0.2	<10	970	0.66	0.20	0.45	0.76	33.80	7.7	25	0.83
CC29613		0.18	0.26	1.65	11.4	<0.2	<10	1000	0.64	0.19	0.19	0.46	34.00	7.2	26	0.92
CC29614		0.08	0.22	1.46	12.2	<0.2	<10	900	0.56	0.19	0.23	0.51	26.90	5.6	24	0.81
CC29615		0.26	0.19	1.45	8.3	<0.2	<10	1000	0.55	0.19	0.20	0.54	29.30	5.4	24	0.85
CC29616		0.20	0.22	1.70	11.4	<0.2	<10	930	0.53	0.24	0.21	0.52	31.10	6.7	28	1.07
CC29617		0.10	0.23	1.19	5.1	<0.2	<10	790	0.34	0.13	0.36	0.47	18.95	3.8	21	1.05
CC29618		0.18	0.28	1.65	10.2	<0.2	<10	1190	0.58	0.23	0.26	0.92	32.80	7.0	28	1.05
CC29619		0.10	0.21	1.59	12.4	<0.2	<10	890	0.57	0.20	0.22	0.32	25.50	7.2	25	1.14
CC29620		0.10	0.25	0.35	15.0	<0.2	10	410	0.24	0.13	0.38	1.48	7.35	2.8	8	0.61
CC29621		0.14	0.33	0.42	19.3	<0.2	10	390	0.41	0.16	0.18	1.41	11.25	3.6	9	0.64
CC29622		0.14	0.47	0.52	19.1	<0.2	10	510	0.56	0.17	0.25	3.00	11.85	2.2	10	0.63
CC29623		0.12	0.57	0.54	16.1	<0.2	10	670	0.48	0.16	0.28	3.27	10.65	1.5	12	0.65
CC29624		0.12	0.97	0.65	16.5	<0.2	10	670	0.52	0.17	0.35	7.68	10.80	5.8	20	0.70
CC29625		0.08	4.28	0.74	31.4	<0.2	<10	920	1.08	0.22	3.23	8.43	26.20	6.2	160	0.48
CC29626		0.10	3.27	0.71	44.3	<0.2	<10	1030	1.06	0.22	1.27	10.55	36.60	5.3	156	0.49
CC29627		0.16	1.73	0.64	30.6	<0.2	<10	690	1.00	0.28	1.01	6.19	27.20	10.4	164	0.72
CC29628		0.12	2.33	1.47	77.2	<0.2	10	630	1.90	0.28	1.40	26.60	48.20	11.7	126	1.75
CC29629		0.14	4.88	0.81	73.8	<0.2	10	800	1.26	0.25	3.70	31.20	29.10	9.0	78	1.34
CC29630		0.14	3.13	0.47	82.5	<0.2	10	780	1.12	0.26	9.38	32.20	20.50	10.2	57	1.25
CC29631		0.22	2.69	0.27	24.1	<0.2	<10	460	0.43	0.06	3.74	72.90	9.57	1.8	24	0.40
CC29632		0.10	7.60	0.64	103.5	<0.2	20	720	1.11	0.28	5.06	48.30	15.25	9.4	62	1.90
CC29633		0.10	0.40	1.07	35.6	<0.2	<10	470	0.71	0.17	0.87	9.35	15.40	5.8	39	0.59
CC29634		0.14	0.25	1.15	36.9	<0.2	10	750	0.95	0.21	0.61	5.74	17.75	9.7	25	0.64
CC29635		0.12	0.85	0.45	39.4	<0.2	<10	560	0.71	0.20	0.51	5.17	18.45	10.2	15	0.70
CC29636		0.12	0.42	0.58	38.9	<0.2	<10	420	0.46	0.21	0.22	3.55	9.13	9.5	17	0.96
CC29637		0.10	0.32	0.48	19.8	<0.2	10	380	0.34	0.20	0.05	0.25	9.58	1.4	13	0.60
CC29638		0.10	0.40	0.41	17.8	<0.2	10	460	0.32	0.16	0.75	2.44	9.49	3.2	10	0.72

Comments: Gold determinations by ME-MS41 are semi-quantitative due to the small sample weight used (0.5g).

ALS Chemex

EXCELLENCE IN ANALYTICAL CHEMISTRY

ALS Canada Ltd.

212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: STRATEGIC METALS LTD.
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NiMo

Finalized Date: 2-JUL-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07064995

Sample Description	Method	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41
	Analyte	Cu	Fe	Ga	Ge	Hf	Hg	In	K	La	Li	Mg	Mn	Mo	Na	Nb
	Units	ppm	%	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	%	ppm	ppm	%	ppm
	LOR	0.2	0.01	0.05	0.05	0.02	0.01	0.005	0.01	0.2	0.1	0.01	5	0.05	0.01	0.05
CC29598		14.1	1.80	4.50	0.05	0.03	0.07	0.020	0.05	10.2	9.0	0.25	100	4.51	<0.01	0.43
CC29599		13.7	1.90	4.31	0.05	0.03	0.07	0.020	0.06	10.2	9.9	0.25	101	3.91	<0.01	0.45
CC29600		25.6	1.46	1.33	0.05	0.02	0.04	0.017	0.08	5.6	0.6	0.03	41	28.10	<0.01	0.07
CC29601		41.6	1.39	5.06	0.09	0.13	0.10	0.025	0.12	22.4	19.2	1.15	124	1.44	0.01	0.44
CC29603		33.4	1.47	4.39	0.08	0.10	0.10	0.024	0.10	19.8	19.8	1.08	91	1.58	0.01	0.39
CC29604		32.9	1.52	4.12	0.09	0.14	0.10	0.023	0.12	18.1	19.4	1.21	208	3.20	0.01	0.38
CC29605		36.8	1.98	4.89	0.07	0.15	0.09	0.024	0.10	20.9	20.8	1.01	158	2.05	0.01	0.47
CC29606		41.9	1.44	4.45	0.07	0.15	0.09	0.023	0.11	18.2	19.5	1.08	145	1.56	0.01	0.42
CC29607		31.5	1.74	4.25	0.07	0.12	0.09	0.022	0.08	19.5	19.0	0.87	503	1.90	<0.01	0.39
CC29608		31.7	1.95	4.84	0.08	0.12	0.12	0.026	0.08	21.0	20.4	0.98	184	2.72	0.01	0.44
CC29609		44.0	2.14	4.35	0.09	0.13	0.10	0.024	0.11	16.7	17.8	0.91	241	4.84	0.01	0.54
CC29610		24.9	2.29	5.14	0.07	0.07	0.06	0.029	0.08	16.4	14.6	0.39	187	2.08	<0.01	0.65
CC29611		25.6	2.47	5.23	0.07	0.08	0.06	0.028	0.08	16.1	14.8	0.39	289	2.43	<0.01	0.63
CC29612		24.4	2.21	5.06	0.06	0.06	0.05	0.027	0.07	15.2	13.7	0.35	144	2.86	<0.01	0.62
CC29613		22.2	2.72	5.38	0.07	0.04	0.06	0.027	0.06	15.2	13.4	0.33	150	4.24	<0.01	0.64
CC29614		18.7	2.74	4.94	0.06	0.04	0.06	0.025	0.06	12.2	11.0	0.26	119	4.11	<0.01	0.53
CC29615		19.2	1.88	4.88	0.06	0.04	0.05	0.025	0.05	13.1	12.2	0.30	80	1.07	<0.01	0.52
CC29616		19.7	2.26	5.53	0.05	0.03	0.06	0.030	0.08	16.3	13.2	0.34	126	2.99	<0.01	0.80
CC29617		12.8	1.45	4.73	<0.05	0.02	0.06	0.018	0.05	10.0	7.0	0.19	53	4.42	<0.01	0.64
CC29618		24.2	2.05	5.48	0.05	0.04	0.06	0.032	0.08	17.2	12.8	0.32	96	2.51	<0.01	0.82
CC29619		19.1	2.55	5.31	0.05	0.03	0.06	0.029	0.06	13.5	11.6	0.28	192	7.77	<0.01	0.73
CC29620		22.6	0.83	1.51	0.05	0.02	0.06	0.015	0.07	4.3	0.6	0.03	25	42.00	0.01	0.10
CC29621		32.3	1.12	1.66	0.05	0.02	0.07	0.021	0.08	6.6	0.9	0.03	33	45.30	0.01	0.11
CC29622		36.3	1.11	1.92	0.05	0.02	0.15	0.024	0.07	6.8	1.3	0.05	29	44.50	<0.01	0.14
CC29623		32.2	0.60	2.05	<0.05	0.03	0.19	0.020	0.07	6.2	1.6	0.05	38	16.10	<0.01	0.13
CC29624		42.1	0.85	2.48	<0.05	0.03	0.31	0.018	0.08	6.3	2.5	0.07	159	22.80	<0.01	0.17
CC29625		164.5	1.77	3.33	0.11	0.05	0.51	0.031	0.04	21.4	3.7	0.48	96	15.70	0.01	0.20
CC29626		167.5	1.77	3.97	0.25	0.07	0.72	0.030	0.03	24.9	3.8	0.09	53	35.80	<0.01	0.19
CC29627		141.5	1.88	5.05	0.12	0.05	0.29	0.048	0.06	19.4	4.7	0.09	98	22.70	0.01	0.21
CC29628		127.5	2.08	7.59	0.12	0.09	0.78	0.042	0.09	28.7	8.9	0.23	86	72.30	0.01	0.39
CC29629		140.5	1.91	5.15	0.14	0.11	1.12	0.039	0.08	17.6	5.0	0.64	95	70.90	0.01	0.27
CC29630		118.5	2.00	3.91	0.12	0.16	0.70	0.045	0.11	10.7	2.8	2.55	169	82.70	0.02	0.17
CC29631		88.3	0.41	1.50	0.11	0.07	0.35	0.012	0.03	9.8	0.8	0.06	40	17.05	0.01	0.12
CC29632		158.0	2.14	4.80	0.16	0.18	0.95	0.049	0.16	8.8	2.9	1.35	93	82.50	0.01	0.17
CC29633		50.3	1.91	4.53	0.08	0.05	0.10	0.033	0.05	8.6	5.0	0.10	69	55.30	0.01	0.45
CC29634		42.8	2.29	3.27	0.07	0.07	0.08	0.033	0.07	9.9	3.1	0.09	75	42.00	0.01	0.24
CC29635		61.8	2.48	1.52	0.08	0.09	0.29	0.031	0.08	11.2	1.2	0.03	94	51.40	<0.01	0.11
CC29636		60.0	2.42	2.63	0.07	0.02	0.08	0.033	0.10	5.6	1.3	0.04	70	88.70	<0.01	0.15
CC29637		29.3	2.43	2.60	0.05	0.02	0.08	0.043	0.21	5.8	1.0	0.03	17	32.10	0.01	0.15
CC29638		29.2	1.68	1.98	0.05	0.02	0.11	0.023	0.12	5.4	0.8	0.03	28	34.70	0.02	0.21

Comments: Gold determinations by ME-MS41 are semi-quantitative due to the small sample weight used (0.5g).

ALS Chemex

EXCELLENCE IN ANALYTICAL CHEMISTRY

ALS Canada Ltd.

212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: STRATEGIC METALS LTD.
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NiMo

Finalized Date: 2-JUL-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07064995

Sample Description	Method	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41
	Analyte	Ni	P	Pb	Rb	Re	S	Sb	Sc	Se	Sn	Sr	Ta	Te	Th	Ti
	Units	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%
	LOR	0.2	10	0.2	0.1	0.001	0.01	0.05	0.1	0.2	0.2	0.2	0.01	0.01	0.2	0.005
CC29598		16.9	570	9.7	9.5	0.001	0.05	1.50	2.8	1.6	0.5	18.4	<0.01	0.04	2.2	0.009
CC29599		16.2	550	9.3	10.3	0.001	0.04	1.45	2.8	1.4	0.4	23.1	<0.01	0.05	2.4	0.009
CC29600		93.2	230	8.1	8.1	0.004	0.07	3.09	2.0	3.7	0.3	29.6	<0.01	0.06	1.2	<0.005
CC29601		35.1	1950	10.9	15.5	<0.001	0.04	2.11	4.8	1.3	0.5	100.5	<0.01	0.05	4.8	0.017
CC29603		31.0	1780	9.4	12.9	<0.001	0.06	1.62	3.8	1.4	0.4	117.0	<0.01	0.05	3.4	0.014
CC29604		35.1	2130	8.6	12.8	0.001	0.06	2.26	3.7	1.7	0.4	122.5	<0.01	0.06	3.0	0.014
CC29605		32.2	1690	10.2	13.4	<0.001	0.03	1.89	4.5	1.2	0.4	123.0	<0.01	0.05	4.2	0.016
CC29606		32.8	1820	9.0	12.8	<0.001	0.03	1.70	3.9	1.0	0.4	151.0	<0.01	0.05	4.1	0.017
CC29607		29.0	1640	10.0	11.7	0.001	0.05	1.56	3.6	1.5	0.4	66.2	<0.01	0.05	3.2	0.013
CC29608		26.1	1380	10.3	10.8	<0.001	0.05	1.42	4.0	1.4	0.4	92.5	<0.01	0.05	2.4	0.015
CC29609		38.6	1750	10.6	11.7	<0.001	0.04	2.63	4.2	1.7	0.4	160.5	<0.01	0.06	3.6	0.023
CC29610		28.5	520	13.2	11.0	<0.001	0.02	1.20	4.9	1.3	0.5	36.2	<0.01	0.05	4.7	0.016
CC29611		29.8	550	12.6	11.8	<0.001	0.02	1.31	5.0	1.3	0.5	37.1	<0.01	0.05	4.9	0.016
CC29612		27.3	530	12.5	11.8	<0.001	0.02	1.31	4.5	1.3	0.5	34.9	<0.01	0.05	4.3	0.013
CC29613		23.8	500	12.0	11.5	<0.001	0.02	1.35	4.8	1.5	0.5	23.4	<0.01	0.05	4.1	0.013
CC29614		18.8	500	11.7	9.6	0.001	0.04	1.35	3.8	1.4	0.5	23.5	<0.01	0.06	2.9	0.010
CC29615		20.5	350	12.2	9.3	<0.001	0.02	1.28	4.0	1.2	0.5	22.0	<0.01	0.05	3.9	0.011
CC29616		22.9	550	14.0	14.7	<0.001	0.03	1.19	4.4	1.2	0.6	24.4	<0.01	0.04	4.0	0.015
CC29617		15.9	810	6.1	8.2	<0.001	0.09	0.96	2.7	1.4	0.5	31.0	<0.01	0.04	1.5	0.008
CC29618		27.5	520	13.7	14.4	<0.001	0.04	1.52	4.9	1.5	0.6	31.5	<0.01	0.05	4.6	0.013
CC29619		22.2	650	12.2	12.7	<0.001	0.05	1.68	3.7	1.7	0.6	29.2	<0.01	0.05	2.8	0.011
CC29620		62.1	390	8.6	9.7	0.036	0.10	6.47	1.9	8.1	0.5	43.0	<0.01	0.15	1.1	<0.005
CC29621		73.4	290	10.9	9.6	0.029	0.08	6.82	2.2	4.7	0.5	38.3	<0.01	0.09	1.4	<0.005
CC29622		51.5	300	9.5	9.7	0.022	0.05	6.89	2.5	4.3	0.5	42.2	<0.01	0.11	1.5	<0.005
CC29623		42.1	290	9.3	9.7	0.018	0.06	4.45	2.2	4.5	0.5	36.5	<0.01	0.08	1.2	<0.005
CC29624		67.2	440	8.3	11.2	0.018	0.07	6.92	2.5	4.6	0.6	45.7	<0.01	0.09	1.1	<0.005
CC29625		199.5	1910	10.6	5.8	<0.001	0.10	11.40	5.6	15.0	0.9	158.5	0.01	0.17	1.3	0.006
CC29626		210.0	1760	9.7	5.1	0.004	0.10	9.09	4.8	47.6	0.8	150.0	0.01	0.17	1.3	0.005
CC29627		221.0	2870	11.7	8.7	0.001	0.05	14.90	5.0	15.9	1.1	82.0	0.01	0.19	2.7	0.007
CC29628		251.0	460	22.9	12.7	0.005	0.06	30.20	7.2	14.4	1.1	107.0	0.01	0.22	2.6	0.009
CC29629		241.0	780	21.6	11.4	0.007	0.11	39.10	5.3	20.4	1.0	179.5	0.01	0.21	1.6	0.007
CC29630		285.0	1010	14.7	11.0	0.008	0.05	29.70	5.0	13.5	1.1	429.0	0.01	0.22	3.5	0.005
CC29631		140.5	670	5.5	2.9	0.011	0.20	20.30	3.7	16.3	0.2	284.0	0.01	0.07	0.5	0.006
CC29632		360.0	850	19.4	15.2	0.020	0.08	42.50	6.9	22.2	1.2	182.0	0.01	0.21	4.4	0.006
CC29633		186.0	540	11.9	5.3	0.001	0.08	10.70	4.3	9.0	0.6	56.1	0.01	0.14	1.1	0.009
CC29634		180.0	350	14.0	7.9	<0.001	0.03	6.97	5.4	5.5	0.7	37.8	<0.01	0.09	1.7	<0.005
CC29635		242.0	350	13.5	8.0	0.008	0.04	8.52	6.4	7.6	0.7	42.9	0.01	0.12	2.5	<0.005
CC29636		275.0	350	12.2	12.8	<0.001	0.04	12.90	3.0	7.5	0.8	27.2	<0.01	0.16	1.1	<0.005
CC29637		20.7	160	11.1	15.2	<0.001	0.63	3.82	2.4	7.0	0.7	30.9	<0.01	0.06	2.0	<0.005
CC29638		116.0	390	9.1	9.7	0.004	0.28	4.14	2.5	5.0	0.5	72.5	<0.01	0.07	1.1	0.005

Comments: Gold determinations by ME-MS41 are semi-quantitative due to the small sample weight used (0.5g).

ALS Chemex

EXCELLENCE IN ANALYTICAL CHEMISTRY

ALS Canada Ltd.

212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: STRATEGIC METALS LTD.
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Finalized Date: 2-JUL-2007
Account: MTT

Project: NiMo

CERTIFICATE OF ANALYSIS VA07064995

Sample Description	Method	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	Zn-OG46
	Analyte	Tl	U	V	W	Y	Zn	Zr	Zn
	Units	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%
	LOR	0.02	0.05	1	0.05	0.05	2	0.5	0.01
CC29598		0.24	1.13	98	0.09	5.98	97	0.8	
CC29599		0.24	1.12	90	0.10	5.53	94	0.8	
CC29600		1.34	1.89	100	0.11	11.10	199	0.5	
CC29601		0.17	1.57	122	0.12	19.85	163	5.7	
CC29603		0.14	1.56	106	0.08	18.30	173	3.2	
CC29604		0.14	1.68	99	0.15	16.70	202	4.4	
CC29605		0.15	1.38	111	0.10	17.15	141	5.2	
CC29606		0.15	1.43	106	0.14	15.05	165	5.3	
CC29607		0.14	1.57	101	0.12	15.70	145	3.8	
CC29608		0.15	1.02	93	0.16	18.00	110	3.1	
CC29609		0.18	1.66	91	0.13	15.25	190	4.0	
CC29610		0.22	1.34	75	0.12	11.20	117	2.3	
CC29611		0.25	1.22	79	0.14	11.05	116	2.6	
CC29612		0.25	1.40	77	0.12	10.35	111	1.9	
CC29613		0.25	1.39	86	0.13	9.75	103	1.6	
CC29614		0.21	1.17	87	0.11	8.20	86	1.0	
CC29615		0.24	1.14	79	0.14	7.49	97	1.2	
CC29616		0.29	1.25	95	0.20	7.90	110	1.2	
CC29617		0.35	1.02	72	0.11	5.34	64	1.1	
CC29618		0.35	1.64	109	0.26	10.15	122	1.6	
CC29619		0.35	1.76	111	0.17	7.43	94	1.1	
CC29620		2.04	2.58	133	0.15	5.75	133	0.9	
CC29621		2.03	3.23	175	0.17	12.45	175	0.7	
CC29622		1.80	4.13	225	0.16	12.75	143	1.0	
CC29623		2.02	3.86	181	0.13	10.30	128	1.1	
CC29624		2.40	4.31	298	0.15	13.30	287	1.1	
CC29625		0.70	3.67	213	0.28	32.50	945	1.9	
CC29626		0.71	7.13	215	0.25	39.10	986	2.4	
CC29627		0.64	6.10	277	0.34	27.60	930	2.8	
CC29628		2.11	9.81	1700	0.48	54.00	1890	3.1	
CC29629		3.07	8.28	1145	0.40	46.10	1950	4.3	
CC29630		2.60	10.25	865	0.42	30.10	1960	11.9	
CC29631		1.10	5.16	352	0.11	24.50	3100	3.3	
CC29632		2.55	10.25	1290	0.27	36.80	3830	10.8	
CC29633		3.08	5.58	874	0.28	21.70	736	1.8	
CC29634		1.88	4.45	359	0.21	24.80	483	2.4	
CC29635		2.32	3.58	219	0.23	33.60	511	4.3	
CC29636		3.55	3.33	606	0.30	12.85	683	0.8	
CC29637		2.77	2.25	175	0.13	4.50	48	1.6	
CC29638		1.93	4.12	169	0.18	6.51	178	1.1	

Comments: Gold determinations by ME-MS41 are semi-quantitative due to the small sample weight used (0.5g).

ALS Chemex

EXCELLENCE IN ANALYTICAL CHEMISTRY

ALS Canada Ltd.

212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: STRATEGIC METALS LTD.
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NiMo

Finalized Date: 2-JUL-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07064995

Sample Description	Method	WEI-21	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41
	Analyte	Recvd Wt.	Ag	Al	As	Au	B	Ba	Be	Bi	Ca	Cd	Ce	Co	Cr	Cs
	Units	kg	ppm	%	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppm	ppm	ppm
	LOR	0.02	0.01	0.01	0.1	0.2	10	10	0.05	0.01	0.01	0.01	0.02	0.1	1	0.05
CC29639		0.08	0.22	0.52	17.6	<0.2	<10	540	0.57	0.12	0.28	2.84	11.95	11.8	8	0.50
CC29640		0.10	0.55	0.52	14.1	<0.2	10	1000	0.38	0.10	1.60	2.40	7.19	2.1	11	0.79
CC29641		0.12	0.47	1.37	14.9	<0.2	<10	2120	1.03	0.15	0.91	10.15	22.20	30.7	23	1.16
CC29642		0.10	0.22	0.65	28.7	<0.2	<10	310	0.30	0.17	0.03	0.40	9.02	3.4	15	1.01
CC29643		0.14	0.54	0.91	6.9	<0.2	<10	2520	0.64	0.17	1.15	2.71	28.50	9.1	17	0.74
CC29644		0.16	0.60	0.90	7.2	<0.2	<10	2520	0.64	0.16	1.28	3.00	28.10	6.9	18	0.84
CC29645		0.16	0.57	0.85	8.2	<0.2	<10	1960	0.61	0.15	1.24	4.18	26.60	6.4	17	0.79
CC29646		0.12	0.85	0.83	28.6	<0.2	10	1670	0.91	0.18	2.47	14.10	25.00	12.8	26	1.06
CC29647		0.20	0.51	0.86	26.6	<0.2	10	1800	0.84	0.17	2.17	9.41	22.20	13.6	25	1.17
CC29648		0.16	0.92	0.63	38.6	<0.2	10	1370	0.92	0.16	3.09	17.60	20.90	14.1	28	1.03
CC29671		0.10	0.51	1.02	41.5	<0.2	<10	230	0.24	0.30	0.05	0.66	18.15	2.8	28	0.76
CC29672		0.16	0.90	2.12	22.1	<0.2	<10	180	0.59	0.28	0.05	0.47	26.80	9.8	39	1.43
CC29673		0.12	0.33	1.13	34.2	<0.2	<10	200	0.37	0.28	0.03	0.42	15.50	3.1	28	1.04
CC29674		0.16	0.19	0.41	14.4	<0.2	<10	200	0.46	0.13	0.06	0.69	12.25	1.8	7	0.54
CC29675		0.16	0.35	0.55	17.3	<0.2	10	980	0.66	0.14	0.52	1.19	11.00	3.4	10	0.51
CC29676		0.12	0.38	0.85	50.1	<0.2	<10	270	0.69	0.19	0.05	4.63	16.30	6.6	24	0.78
CC29677		0.16	1.09	1.12	64.3	<0.2	<10	310	0.80	0.21	0.32	2.40	14.00	8.0	33	0.65
CC29678		0.12	11.65	1.03	98.5	<0.2	<10	310	1.18	0.17	0.75	116.00	13.05	4.3	163	1.37
CC29679		0.16	2.96	0.69	66.6	<0.2	10	980	0.89	0.21	2.89	38.00	19.10	8.5	52	0.65
CC29680		0.30	2.31	0.80	71.8	<0.2	10	1280	1.11	0.21	1.94	33.60	21.30	11.1	61	0.65
CC29681		0.10	2.19	0.76	58.0	<0.2	10	1020	1.12	0.19	1.83	23.60	27.30	7.4	82	0.63
CC29682		0.16	0.57	1.01	21.4	<0.2	<10	880	0.67	0.16	1.19	4.58	17.90	5.9	24	0.72
CC29683		0.14	0.67	1.23	22.6	<0.2	<10	790	0.68	0.19	0.96	6.20	21.40	8.2	33	0.80
CC29684		0.18	1.21	1.24	38.6	<0.2	<10	710	0.85	0.20	1.14	9.40	23.60	6.8	49	0.90
CC29685		0.14	1.45	1.27	39.9	<0.2	<10	870	0.96	0.18	1.59	22.00	25.10	7.0	43	0.98
CC29686		0.08	0.67	0.73	37.9	<0.2	<10	590	0.44	0.17	1.58	10.90	14.15	4.5	23	0.66
CC29687		0.16	4.17	1.48	75.0	<0.2	<10	630	1.19	0.22	0.89	68.70	29.50	8.2	73	1.05
CC29688		0.10	1.31	1.13	56.3	<0.2	<10	1570	1.01	0.18	3.69	41.80	27.50	7.7	34	0.59
CC29689		0.10	2.68	1.10	70.6	<0.2	10	1450	0.98	0.22	4.71	22.40	31.10	10.2	43	0.57
CC29690		0.18	3.86	0.65	113.0	<0.2	10	720	0.84	0.25	7.18	49.20	14.10	8.4	48	1.24
CC29691		0.18	3.09	0.94	97.2	<0.2	10	1020	1.29	0.29	1.22	27.70	25.40	12.5	62	0.86
CC29692		0.28	2.68	0.80	45.3	<0.2	10	1090	1.01	0.21	2.56	22.20	24.80	6.1	72	0.72
CC29693		0.30	1.75	0.73	50.7	<0.2	10	990	1.09	0.19	1.49	13.25	31.90	6.7	90	0.66
CC29694		0.14	0.16	0.25	5.4	<0.2	<10	90	0.09	0.09	0.03	0.19	6.39	0.6	7	0.66
CC29695		0.08	0.45	0.55	6.8	<0.2	<10	210	0.27	0.08	0.21	1.72	15.00	2.2	27	0.94
CC29696		0.14	0.14	1.14	20.4	<0.2	<10	190	0.30	0.23	0.11	0.79	23.90	5.1	27	0.76
CC29697		0.10	0.58	0.80	11.0	<0.2	<10	3140	0.62	0.20	0.59	1.23	17.85	10.4	20	0.45
CC29698		0.20	0.40	1.02	12.1	<0.2	<10	3030	0.65	0.22	0.16	0.69	22.50	9.1	19	0.57
CC29699		0.12	0.44	0.86	11.1	<0.2	<10	3170	0.56	0.21	0.40	0.51	18.45	8.3	16	0.58
CC29700		0.10	0.42	1.48	12.4	<0.2	10	5060	1.02	0.22	0.52	1.62	39.30	8.8	24	0.95

Comments: Gold determinations by ME-MS41 are semi-quantitative due to the small sample weight used (0.5g).

ALS Chemex

EXCELLENCE IN ANALYTICAL CHEMISTRY

ALS Canada Ltd.

212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NiMo

Finalized Date: 2-JUL-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07064995

Sample Description	Method	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41
	Analyte	Cu	Fe	Ga	Ge	Hf	Hg	In	K	La	Li	Mg	Mn	Mo	Na	Nb
	Units	ppm	%	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	%	ppm	ppm	%	ppm
	LOR	0.2	0.01	0.05	0.05	0.02	0.01	0.005	0.01	0.2	0.1	0.01	5	0.05	0.01	0.05
CC29639		32.7	1.86	1.53	0.05	0.03	0.08	0.023	0.08	6.1	1.0	0.03	66	41.70	0.01	0.13
CC29640		47.0	1.07	1.58	0.11	0.07	0.15	0.015	0.06	3.7	1.0	0.09	25	22.80	0.02	0.14
CC29641		161.5	3.41	3.09	0.08	0.08	0.13	0.030	0.11	12.1	10.3	0.39	492	8.41	0.02	0.27
CC29642		35.5	11.45	2.73	0.12	0.05	0.05	0.033	0.13	4.2	7.0	0.13	46	14.40	0.02	0.27
CC29643		41.4	1.81	2.84	0.06	0.08	0.15	0.027	0.10	15.5	9.8	0.38	476	4.74	0.02	0.31
CC29644		44.7	1.51	2.89	0.06	0.07	0.17	0.026	0.10	15.7	9.2	0.35	216	4.87	0.02	0.34
CC29645		45.1	1.52	2.79	0.06	0.07	0.17	0.025	0.09	14.3	9.0	0.35	228	7.75	0.02	0.33
CC29646		81.4	2.32	2.99	0.08	0.07	0.24	0.038	0.13	13.7	8.6	0.83	313	23.60	0.02	0.25
CC29647		62.9	2.51	3.08	0.08	0.08	0.14	0.040	0.14	11.4	9.3	0.87	273	21.00	0.02	0.16
CC29648		83.8	2.34	2.51	0.10	0.12	0.23	0.039	0.13	11.1	5.3	1.04	260	38.30	0.01	0.17
CC29671		22.0	3.42	9.26	0.06	<0.02	0.03	0.029	0.07	9.6	2.4	0.08	74	26.20	<0.01	1.58
CC29672		36.4	3.61	7.50	0.06	<0.02	0.05	0.038	0.09	13.6	25.2	0.34	224	13.10	<0.01	1.36
CC29673		37.0	3.28	7.31	0.08	<0.02	0.07	0.046	0.11	8.5	8.7	0.13	77	44.20	<0.01	0.86
CC29674		32.6	1.73	1.33	<0.05	0.04	0.07	0.020	0.07	6.4	1.4	0.03	16	23.20	<0.01	0.12
CC29675		34.3	1.24	1.85	<0.05	0.07	0.13	0.027	0.07	6.0	2.7	0.07	58	28.60	0.01	0.17
CC29676		64.7	2.29	2.96	0.08	0.05	0.12	0.031	0.06	9.5	6.5	0.07	72	70.60	<0.01	0.29
CC29677		50.5	2.72	3.10	0.08	0.05	0.19	0.042	0.05	7.6	7.0	0.09	115	71.50	0.01	0.32
CC29678		227.0	1.28	6.10	0.19	0.11	1.50	0.030	0.14	15.0	3.0	0.08	70	89.80	0.01	0.15
CC29679		109.0	1.41	3.47	0.10	0.11	0.51	0.030	0.09	13.1	3.5	0.70	153	24.30	0.02	0.23
CC29680		106.0	1.61	3.82	0.09	0.14	0.41	0.029	0.09	13.2	4.2	0.38	131	25.30	0.01	0.24
CC29681		111.5	1.59	3.84	0.10	0.12	0.44	0.030	0.08	17.7	4.7	0.14	172	23.00	0.01	0.23
CC29682		34.2	1.75	3.35	0.05	0.09	0.11	0.025	0.06	9.9	6.9	0.17	158	22.60	0.01	0.43
CC29683		33.3	1.80	4.27	0.06	0.10	0.15	0.028	0.07	11.8	10.0	0.27	264	15.40	0.01	0.49
CC29684		52.2	1.82	4.62	0.07	0.11	0.30	0.031	0.08	14.6	9.7	0.26	174	17.60	0.01	0.47
CC29685		72.9	1.84	4.26	0.09	0.13	0.33	0.029	0.07	17.4	9.1	0.26	178	22.20	0.02	0.50
CC29686		32.2	1.73	3.11	0.06	0.07	0.09	0.026	0.04	7.8	5.2	0.10	63	32.10	0.01	0.48
CC29687		123.5	2.45	5.47	0.12	0.15	0.76	0.034	0.10	23.2	11.1	0.30	207	52.40	0.01	0.51
CC29688		96.4	1.87	3.90	0.11	0.11	0.37	0.026	0.06	20.6	6.7	0.23	223	51.50	0.02	0.43
CC29689		86.6	2.10	4.24	0.16	0.14	0.31	0.032	0.13	20.2	8.4	0.31	229	61.10	0.02	0.39
CC29690		126.5	1.82	4.54	0.13	0.27	0.61	0.037	0.13	7.9	3.0	1.50	90	102.50	0.02	0.14
CC29691		127.5	2.48	4.80	0.11	0.15	0.52	0.043	0.11	14.9	5.4	0.25	161	79.80	0.01	0.23
CC29692		122.0	1.63	3.99	0.09	0.14	0.56	0.031	0.09	15.7	4.9	0.63	75	32.90	0.02	0.25
CC29693		112.5	1.68	4.20	0.11	0.10	0.40	0.029	0.08	20.7	4.4	0.12	192	29.80	0.01	0.19
CC29694		4.6	0.30	2.98	<0.05	<0.02	0.01	<0.005	0.04	3.5	0.3	0.02	11	6.54	<0.01	0.11
CC29695		16.2	0.72	2.94	<0.05	<0.02	0.07	0.012	0.06	8.2	1.7	0.05	41	13.75	0.01	0.22
CC29696		17.4	2.44	5.45	0.05	0.02	0.02	0.022	0.08	12.4	8.9	0.21	124	17.55	0.01	0.77
CC29697		40.5	2.91	2.36	0.06	0.07	0.15	0.038	0.10	8.6	4.8	0.16	345	5.17	0.03	0.21
CC29698		46.9	3.14	2.76	0.06	0.06	0.21	0.038	0.11	11.2	6.7	0.16	145	3.84	0.02	0.28
CC29699		34.1	2.64	2.59	0.05	0.07	0.15	0.038	0.10	8.8	5.2	0.15	200	4.40	0.02	0.23
CC29700		38.3	2.76	4.36	0.07	0.09	0.11	0.043	0.08	22.0	7.6	0.23	102	6.06	0.04	0.34

Comments: Gold determinations by ME-MS41 are semi-quantitative due to the small sample weight used (0.5g).

ALS Chemex

EXCELLENCE IN ANALYTICAL CHEMISTRY

ALS Canada Ltd.

212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NiMo

Finalized Date: 2-JUL-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07064995

Sample Description	Method	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41
	Analyte	Ni	P	Pb	Rb	Re	S	Sb	Sc	Se	Sn	Sr	Ta	Te	Th	Ti
	Units	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%
	LOR	0.2	10	0.2	0.1	0.001	0.01	0.05	0.1	0.2	0.2	0.2	0.01	0.01	0.2	0.005
CC29639		188.5	400	8.3	8.7	0.009	0.12	3.63	2.9	5.8	0.3	83.2	<0.01	0.07	0.9	<0.005
CC29640		111.5	640	5.9	6.6	0.021	0.22	3.09	3.6	30.8	0.3	101.0	<0.01	0.05	0.7	<0.005
CC29641		114.0	940	10.2	12.0	0.016	0.19	2.99	4.8	5.3	0.4	93.1	<0.01	0.05	3.1	0.006
CC29642		28.7	530	12.9	9.4	0.011	0.86	3.29	3.7	5.4	0.4	35.6	<0.01	0.06	2.7	<0.005
CC29643		47.9	1010	10.0	10.2	0.004	0.13	1.89	3.6	2.8	0.3	79.5	<0.01	0.04	2.6	0.008
CC29644		46.6	990	10.4	10.8	0.006	0.15	2.16	3.6	3.3	0.3	88.3	<0.01	0.04	2.3	0.008
CC29645		59.5	950	9.9	10.2	0.009	0.15	2.31	3.4	3.6	0.4	87.8	<0.01	0.03	2.1	0.008
CC29646		145.0	1340	12.7	12.2	0.033	0.24	7.07	4.7	8.7	0.5	169.0	<0.01	0.09	2.5	0.006
CC29647		107.0	1560	12.3	12.0	0.024	0.21	5.25	4.7	6.0	0.5	182.5	<0.01	0.09	3.5	<0.005
CC29648		151.0	1350	11.8	11.0	0.052	0.28	10.75	5.2	11.6	0.5	219.0	<0.01	0.12	3.5	<0.005
CC29671		17.9	640	13.3	8.3	<0.001	0.07	15.20	2.1	5.8	1.1	31.0	<0.01	0.17	1.8	0.040
CC29672		45.3	480	12.4	16.4	<0.001	0.04	6.00	3.8	3.6	0.8	14.2	<0.01	0.10	2.8	0.041
CC29673		22.1	400	15.3	14.7	<0.001	0.14	15.65	2.3	14.4	1.0	47.0	<0.01	0.25	2.2	0.020
CC29674		31.2	180	8.3	7.6	0.008	0.04	2.63	2.9	2.4	0.3	24.5	<0.01	0.06	2.1	<0.005
CC29675		56.8	270	8.9	7.7	0.008	0.04	3.93	3.1	3.4	0.4	53.7	<0.01	0.07	1.8	<0.005
CC29676		259.0	390	11.0	8.5	0.007	0.03	13.40	3.0	7.8	0.5	11.1	<0.01	0.17	1.2	0.008
CC29677		356.0	570	14.7	8.5	0.010	0.05	12.15	2.5	9.7	0.6	21.1	<0.01	0.17	1.0	0.008
CC29678		493.0	800	20.2	16.0	0.003	0.11	89.40	6.5	26.7	0.5	102.0	0.01	0.35	0.5	0.009
CC29679		249.0	1140	13.9	9.4	0.017	0.13	25.40	4.3	12.3	0.7	150.0	0.01	0.18	1.6	0.007
CC29680		239.0	1060	16.9	10.3	0.010	0.11	25.90	5.0	8.4	0.7	125.0	0.01	0.20	2.6	0.008
CC29681		221.0	1520	14.0	9.8	0.011	0.09	19.95	4.2	8.3	0.7	120.0	0.01	0.20	1.8	0.008
CC29682		94.5	560	10.0	9.0	0.005	0.07	6.92	3.1	6.1	0.5	79.1	<0.01	0.09	1.5	0.010
CC29683		87.0	660	11.6	10.7	0.005	0.05	7.09	3.7	4.8	0.5	66.8	<0.01	0.09	2.1	0.013
CC29684		108.5	620	13.0	12.2	0.006	0.06	13.65	4.5	5.4	0.6	70.9	<0.01	0.13	2.3	0.012
CC29685		254.0	660	11.2	10.5	0.007	0.08	13.65	4.7	9.0	0.5	82.0	0.01	0.12	1.7	0.012
CC29686		151.0	560	11.4	7.1	0.003	0.09	11.65	2.1	9.1	0.5	82.1	<0.01	0.11	1.0	0.013
CC29687		396.0	950	18.4	12.2	0.004	0.07	30.60	8.4	15.0	0.6	85.4	0.01	0.17	2.1	0.017
CC29688		376.0	1030	12.6	7.3	0.005	0.11	14.85	3.0	13.4	0.6	132.0	0.01	0.13	0.8	0.009
CC29689		215.0	1230	16.8	9.7	0.004	0.09	26.00	4.2	29.5	0.7	180.5	0.01	0.18	2.0	0.011
CC29690		322.0	1070	16.4	12.9	0.008	0.05	39.40	4.8	14.5	0.9	321.0	<0.01	0.21	4.4	0.007
CC29691		338.0	810	19.4	11.8	0.004	0.05	31.00	6.3	10.1	1.0	83.6	0.01	0.26	3.6	0.008
CC29692		278.0	960	12.3	10.1	0.003	0.08	18.50	5.4	6.6	0.8	151.5	0.01	0.18	2.4	0.008
CC29693		184.5	2290	11.5	10.2	0.004	0.08	13.25	4.0	5.6	0.8	125.5	0.01	0.17	2.2	0.007
CC29694		5.6	130	5.0	6.6	<0.001	0.01	2.87	0.6	0.9	0.5	11.4	<0.01	0.07	0.3	0.007
CC29695		39.0	620	6.2	6.3	0.001	0.04	1.82	1.5	1.9	0.4	18.8	<0.01	0.05	0.6	0.009
CC29696		53.8	240	11.1	9.5	0.001	0.03	3.64	2.5	2.5	0.6	15.3	<0.01	0.07	2.5	0.025
CC29697		44.3	550	10.5	8.3	0.001	0.05	2.07	3.8	2.9	0.3	49.1	<0.01	0.05	2.3	0.005
CC29698		33.9	490	11.1	10.1	0.001	0.02	1.36	5.2	2.1	0.4	17.5	<0.01	0.05	4.0	0.007
CC29699		27.8	540	12.0	9.6	0.001	0.05	1.89	4.1	1.8	0.3	28.7	<0.01	0.05	2.5	0.005
CC29700		49.8	350	13.9	12.0	<0.001	0.03	2.06	5.2	2.1	0.6	46.6	<0.01	0.07	3.7	0.006

Comments: Gold determinations by ME-MS41 are semi-quantitative due to the small sample weight used (0.5g).

ALS Chemex

EXCELLENCE IN ANALYTICAL CHEMISTRY

ALS Canada Ltd.

212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: STRATEGIC METALS LTD.
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Finalized Date: 2-JUL-2007
Account: MTT

Project: NiMo

CERTIFICATE OF ANALYSIS VA07064995

Sample Description	Method	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	Zn-OG46
	Analyte	Tl	U	V	W	Y	Zn	Zr	Zn
	Units	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%
	LOR	0.02	0.05	1	0.05	0.05	2	0.5	0.01
CC29639		1.58	3.72	141	0.18	24.90	419	0.8	
CC29640		1.40	5.92	120	0.12	7.38	129	3.4	
CC29641		0.77	5.05	159	0.09	22.00	504	3.1	
CC29642		0.96	1.39	130	0.07	5.38	134	3.0	
CC29643		0.34	1.88	76	0.08	16.35	247	2.5	
CC29644		0.37	2.56	100	0.10	17.60	262	2.4	
CC29645		0.77	2.73	101	0.10	16.95	342	2.4	
CC29646		1.50	5.84	244	0.14	24.40	702	2.9	
CC29647		1.18	5.38	210	0.18	19.60	579	4.4	
CC29648		1.50	7.85	315	0.17	26.40	951	7.1	
CC29671		0.86	1.21	525	0.29	3.37	75	0.5	
CC29672		0.73	1.22	228	0.21	4.28	125	0.6	
CC29673		3.03	2.07	510	0.25	4.02	79	0.7	
CC29674		0.88	2.67	85	0.10	9.03	61	1.0	
CC29675		1.09	2.90	145	0.15	10.05	144	1.7	
CC29676		3.43	2.83	580	0.32	22.80	650	0.9	
CC29677		3.89	3.43	420	0.34	18.90	585	1.1	
CC29678		8.59	7.17	2550	0.47	40.70	>10000	2.7	1.14
CC29679		1.76	8.74	1130	0.23	38.10	2760	3.5	
CC29680		1.84	8.24	1280	0.27	36.00	2240	4.5	
CC29681		1.25	7.17	955	0.26	38.30	1880	3.8	
CC29682		1.42	2.50	279	0.17	13.65	503	2.2	
CC29683		1.44	3.11	430	0.19	13.30	765	2.4	
CC29684		2.40	5.63	873	0.21	21.40	1410	2.9	
CC29685		2.52	8.49	670	0.20	34.30	2300	3.2	
CC29686		1.75	3.08	422	0.22	9.58	652	2.1	
CC29687		3.83	5.09	1140	0.33	41.20	8060	3.7	
CC29688		1.67	6.55	543	0.23	40.00	4010	2.9	
CC29689		1.48	5.69	711	0.37	35.50	1590	3.7	
CC29690		2.44	10.30	1270	0.33	28.80	3590	11.5	
CC29691		1.99	5.76	1200	0.37	42.30	2620	4.5	
CC29692		1.53	5.51	854	0.31	37.00	1955	4.9	
CC29693		1.03	6.53	752	0.32	35.40	1275	3.3	
CC29694		1.06	0.74	141	0.09	1.70	23	<0.5	
CC29695		0.70	1.11	104	0.12	4.87	95	<0.5	
CC29696		0.97	0.90	237	0.24	4.33	204	0.6	
CC29697		0.13	1.72	50	0.08	12.90	193	1.5	
CC29698		0.14	1.64	42	0.07	15.60	148	1.5	
CC29699		0.14	1.45	52	0.07	11.20	115	1.4	
CC29700		0.21	2.41	94	0.10	24.20	159	2.1	

Comments: Gold determinations by ME-MS41 are semi-quantitative due to the small sample weight used (0.5g).

ALS Chemex
EXCELLENCE IN ANALYTICAL CHEMISTRY
ALS Canada Ltd.
212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: STRATEGIC METALS LTD.
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Finalized Date: 2-JUL-2007
Account: MTT

Project: NiMo

CERTIFICATE OF ANALYSIS VA07064995

Sample Description	Method / Analyte / Units / LOR	WEI-21 Recvd Wt. kg 0.02	ME-MS41 Ag ppm 0.01	ME-MS41 Al % 0.01	ME-MS41 As ppm 0.1	ME-MS41 Au ppm 0.2	ME-MS41 B ppm 10	ME-MS41 Ba ppm 10	ME-MS41 Be ppm 0.05	ME-MS41 Bi ppm 0.01	ME-MS41 Ca % 0.01	ME-MS41 Cd ppm 0.01	ME-MS41 Ce ppm 0.02	ME-MS41 Co ppm 0.1	ME-MS41 Cr ppm 1	ME-MS41 Cs ppm 0.05
CC29701		0.16	0.20	0.58	21.0	<0.2	<10	360	0.40	0.15	1.35	1.83	11.20	4.5	18	0.61
CC29702		0.10	0.64	0.59	8.0	<0.2	<10	510	0.35	0.08	3.02	4.00	10.15	2.1	17	0.38
CC29703		0.10	0.25	0.51	15.5	<0.2	<10	230	0.19	0.16	0.12	2.31	16.85	2.1	37	0.79
CC29704		0.14	0.37	0.77	74.6	<0.2	<10	190	0.30	0.26	0.05	0.71	12.35	4.5	35	0.63
CC29705		0.12	0.81	0.82	73.5	<0.2	10	290	0.75	0.15	0.29	21.30	15.55	2.2	151	1.00
CC29706		0.08	0.36	0.28	4.8	<0.2	<10	700	0.12	0.04	3.75	9.13	2.96	1.4	6	0.14
CC29707		0.10	1.23	0.68	24.8	<0.2	<10	1460	0.66	0.08	4.16	64.00	14.50	3.7	26	0.45
CC29708		0.14	3.68	1.00	78.8	<0.2	10	1320	1.07	0.24	1.69	39.50	30.80	10.4	75	0.96
CC29709		0.12	2.82	0.88	45.5	<0.2	10	1180	0.91	0.19	2.07	11.35	27.80	6.6	77	0.78
CC29710		0.08	0.85	0.62	21.5	<0.2	<10	1430	0.65	0.11	2.58	7.50	19.95	4.3	41	0.51
CC29711		0.26	0.74	0.75	27.9	<0.2	<10	2260	0.73	0.15	1.17	8.22	29.70	4.1	35	0.57
CC29712		0.16	0.40	0.59	17.2	<0.2	<10	4300	0.50	0.13	1.38	5.13	15.20	3.3	22	0.50
CC29713		0.14	0.19	0.47	11.4	<0.2	<10	6730	0.35	0.11	1.45	3.75	10.65	4.3	21	0.44

Comments: Gold determinations by ME-MS41 are semi-quantitative due to the small sample weight used (0.5g).

ALS Chemex
EXCELLENCE IN ANALYTICAL CHEMISTRY
ALS Canada Ltd.
212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: STRATEGIC METALS LTD.
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NiMo

CERTIFICATE OF ANALYSIS VA07064995

Sample Description	Method Analyte Units LOR	ME-MS41 Cu ppm 0.2	ME-MS41 Fe % 0.01	ME-MS41 Ga ppm 0.05	ME-MS41 Ge ppm 0.05	ME-MS41 Hf ppm 0.02	ME-MS41 Hg ppm 0.01	ME-MS41 In ppm 0.005	ME-MS41 K % 0.01	ME-MS41 La ppm 0.2	ME-MS41 Li ppm 0.1	ME-MS41 Mg % 0.01	ME-MS41 Mn ppm 5	ME-MS41 Mo ppm 0.05	ME-MS41 Na % 0.01	ME-MS41 Nb ppm 0.05
CC29701		27.9	1.53	2.74	<0.05	0.05	0.06	0.020	0.05	6.2	3.5	0.09	90	24.90	0.01	0.42
CC29702		18.4	0.69	1.69	0.06	0.09	0.15	0.012	0.03	6.6	1.9	0.06	47	6.67	0.02	0.27
CC29703		20.0	1.00	4.06	<0.05	<0.02	0.04	0.016	0.04	9.4	0.9	0.03	45	17.70	0.01	0.28
CC29704		43.5	2.89	5.12	0.07	0.02	0.05	0.041	0.07	6.6	2.2	0.05	60	62.50	<0.01	0.48
CC29705		95.6	1.16	5.70	0.15	0.03	0.09	0.022	0.13	15.8	3.3	0.07	60	43.80	0.01	0.19
CC29706		12.1	0.24	0.73	<0.05	0.05	0.10	0.005	0.02	1.9	0.4	0.03	221	1.74	0.02	0.13
CC29707		73.5	0.84	2.27	0.09	0.12	0.34	0.013	0.03	15.7	3.0	0.10	130	13.15	0.02	0.34
CC29708		115.0	2.19	4.60	0.15	0.15	0.59	0.033	0.11	19.3	7.0	0.30	196	67.90	0.02	0.36
CC29709		93.8	1.70	4.09	0.10	0.14	0.60	0.029	0.07	17.8	6.4	0.21	138	32.30	0.02	0.32
CC29710		50.1	1.00	2.47	0.07	0.11	0.25	0.016	0.03	12.4	3.5	0.17	357	19.75	0.02	0.23
CC29711		54.6	1.51	2.97	0.06	0.11	0.24	0.022	0.05	18.9	5.6	0.17	125	38.10	0.02	0.31
CC29712		37.5	1.20	2.57	0.05	0.10	0.13	0.019	0.04	8.6	3.6	0.16	126	30.50	0.03	0.27
CC29713		22.9	1.17	1.95	<0.05	0.08	0.09	0.015	0.04	5.0	2.3	0.20	124	30.90	0.05	0.25

Comments: Gold determinations by ME-MS41 are semi-quantitative due to the small sample weight used (0.5g).

ALS Chemex
EXCELLENCE IN ANALYTICAL CHEMISTRY
ALS Canada Ltd.
212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: STRATEGIC METALS LTD.
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NiMo

Finalized Date: 2-JUL-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07064995

Sample Description	Method	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41
	Analyte	Ni	P	Pb	Rb	Re	S	Sb	Sc	Se	Sn	Sr	Ta	Te	Th	Ti
	Units	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%
	LOR	0.2	10	0.2	0.1	0.001	0.01	0.05	0.1	0.2	0.2	0.2	0.01	0.01	0.2	0.005
CC29701		78.4	400	9.6	7.9	0.005	0.07	4.61	2.2	4.9	0.5	73.1	<0.01	0.09	1.1	0.013
CC29702		43.7	900	4.6	2.9	0.003	0.16	3.63	1.9	7.0	0.2	170.0	0.01	0.04	0.5	0.009
CC29703		61.7	390	8.1	4.1	0.002	0.03	5.79	0.9	4.7	0.8	11.4	<0.01	0.11	0.3	0.013
CC29704		184.0	470	16.9	8.7	0.003	0.07	17.15	1.6	12.2	1.3	12.2	<0.01	0.23	0.7	0.016
CC29705		140.5	390	16.1	16.0	0.002	0.06	62.40	3.1	25.5	0.5	35.6	<0.01	0.30	0.6	0.011
CC29706		22.1	760	2.2	1.0	0.004	0.20	2.48	0.5	6.6	<0.2	128.5	0.01	0.02	<0.2	0.006
CC29707		135.5	870	6.7	3.9	0.009	0.19	11.40	1.9	14.9	0.3	202.0	0.01	0.08	0.4	0.010
CC29708		272.0	950	18.0	11.5	0.005	0.08	31.80	6.3	24.4	0.7	118.0	0.01	0.21	2.7	0.013
CC29709		145.0	1150	10.9	9.6	0.005	0.09	16.00	5.3	11.6	0.7	131.5	0.01	0.15	1.9	0.010
CC29710		121.5	1020	7.2	4.5	0.004	0.15	7.90	2.0	8.9	0.4	151.5	<0.01	0.09	0.8	0.006
CC29711		129.5	650	9.0	7.2	<0.001	0.09	8.60	3.1	5.0	0.6	89.6	<0.01	0.09	1.5	0.010
CC29712		92.3	700	7.9	6.1	<0.001	0.11	5.04	2.4	3.2	0.5	113.5	<0.01	0.07	1.0	0.008
CC29713		55.0	720	6.9	5.2	<0.001	0.10	4.30	1.9	2.1	0.4	219.0	<0.01	0.06	0.8	0.009

Comments: Gold determinations by ME-MS41 are semi-quantitative due to the small sample weight used (0.5g).

ALS Chemex

EXCELLENCE IN ANALYTICAL CHEMISTRY

ALS Canada Ltd.

212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Finalized Date: 2-JUL-2007
Account: MTT

Project: NiMo

CERTIFICATE OF ANALYSIS VA07064995

Sample Description	Method	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	Zn-OG46
	Analyte	Tl	U	V	W	Y	Zn	Zr	Zn
	Units	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%
	LOR	0.02	0.05	1	0.05	0.05	2	0.5	0.01
CC29701		0.83	1.74	197	0.18	8.25	222	1.4	
CC29702		0.76	3.44	128	0.08	16.80	101	2.7	
CC29703		1.09	1.02	234	0.19	2.99	131	<0.5	
CC29704		3.56	1.51	496	0.35	3.25	294	<0.5	
CC29705		4.39	4.23	2600	0.41	21.80	1060	0.6	
CC29706		0.29	2.04	281	<0.05	3.71	249	1.6	
CC29707		0.88	16.95	416	0.14	37.30	1185	3.9	
CC29708		2.53	7.25	1150	0.35	41.90	3150	4.2	
CC29709		1.75	6.51	689	0.33	34.00	1290	4.2	
CC29710		0.74	4.86	342	0.16	17.70	605	3.4	
CC29711		1.17	8.69	446	0.23	23.10	461	3.2	
CC29712		0.71	6.22	289	0.21	13.60	348	3.0	
CC29713		0.26	3.42	140	0.14	10.35	212	2.3	

Comments: Gold determinations by ME-MS41 are semi-quantitative due to the small sample weight used (0.5g).

ALS Chemex
EXCELLENCE IN ANALYTICAL CHEMISTRY
ALS Canada Ltd.
212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Finalized Date: 30-JUN-2007
Account: MTT

CERTIFICATE VA07060911

Project: NIMO

P.O. No.:

This report is for 33 Rock samples submitted to our lab in Vancouver, BC, Canada on 13-JUN-2007.

The following have access to data associated with this certificate:

AL ARCHER VANCOUVER OFFICE	DOUG EATON BILL WENGZYNOWSKI	JOAN MARIACHER

SAMPLE PREPARATION

ALS CODE	DESCRIPTION
WEI-21	Received Sample Weight
LOG-22	Sample login - Rcd w/o BarCode
CRU-QC	Crushing QC Test
CRU-31	Fine crushing - 70% <2mm
SPL-21	Split sample - riffle splitter
PUL-32	Pulverize 1000g to 85% < 75 um
BAG-01	Bulk Master for Storage

ANALYTICAL PROCEDURES

ALS CODE	DESCRIPTION	
ME-MS61	48 element four acid ICP-MS	
Hg-CV41	Trace Hg - cold vapor/AAS	FIMS
Ni-AA62	Ore grade Ni - four acid / AA	AAS
Zn-AA62	Ore grade Zn - four acid / AAS	AAS
PGM-ICP23	Pt, Pd, Au 30g FA ICP	ICP-AES

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

This is the Final Report and supersedes any preliminary report with this certificate number. Results apply to samples as submitted. All pages of this report have been checked and approved for release.

Signature:

Lawrence Ng, Laboratory Manager - Vancouver

ALS Chemex

EXCELLENCE IN ANALYTICAL CHEMISTRY

ALS Canada Ltd.

212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: STRATEGIC METALS LTD.
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO

Finalized Date: 30-JUN-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07060911

Sample Description	Method	WEI-21	PGM-ICP23	PGM-ICP23	PGM-ICP23	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61
	Analyte	Recvd Wt.	Au	Pt	Pd	Ag	Al	As	Ba	Be	Bi	Ca	Cd	Ce	Co	Cr
	Units	kg	ppm	ppm	ppm	ppm	%	ppm	ppm	ppm	ppm	%	ppm	ppm	ppm	ppm
	LOR	0.02	0.001	0.005	0.001	0.01	0.01	0.2	10	0.05	0.01	0.01	0.02	0.01	0.1	1
C385601		2.20	0.121	0.300	0.163	1.43	1.02	5280.0	120	0.22	0.74	0.81	50.30	63.50	176.5	33
C385602		1.16	0.002	<0.005	0.002	0.37	8.31	61.6	330	3.59	0.25	0.05	0.81	37.30	6.0	89
C385603		2.16	0.153	0.321	0.174	2.48	1.16	3570.0	80	0.36	0.65	0.27	1.93	53.60	84.2	38
C385604		1.44	0.004	0.006	0.002	0.34	6.29	129.5	310	2.92	0.20	0.25	1.33	29.00	3.5	77
C385605		4.46	0.095	0.241	0.129	1.72	0.94	5680.0	40	0.28	0.44	0.33	24.70	26.10	131.0	31
C385606		2.08	0.002	<0.005	<0.001	0.29	5.14	64.5	130	2.33	0.15	0.05	1.94	2.98	6.7	67
C385607		3.64	0.103	0.259	0.143	2.32	0.64	5060.0	70	0.24	0.53	0.31	7.64	12.05	115.5	25
C385608		1.64	0.003	0.006	0.002	0.33	7.33	65.3	730	3.45	0.20	0.02	0.35	37.90	2.4	74
C385609		1.60	0.110	0.285	0.154	2.06	1.92	3290.0	70	0.76	0.59	0.08	<0.02	19.25	66.5	43
C385610		0.84	0.006	0.011	0.006	0.40	7.82	135.0	440	3.07	0.22	0.01	<0.02	39.00	3.2	90
C385611		3.08	0.090	0.240	0.131	1.49	1.00	4750.0	70	0.38	0.45	0.20	16.60	19.65	125.0	37
C385612		0.92	0.005	<0.005	0.002	0.47	8.07	65.4	410	3.73	0.25	0.02	0.37	43.90	4.7	92
C385613		0.96	0.165	0.322	0.214	2.27	5.57	90.7	530	1.89	0.85	0.07	<0.02	83.90	1.0	110
C385614		0.90	0.001	0.014	0.003	0.13	2.50	263	170	1.38	0.03	20.10	56.80	23.10	79.1	55
C385615		0.62	0.155	0.368	0.245	2.05	3.25	64.2	160	1.24	0.66	0.19	3.22	26.10	6.0	95
C385616		1.90	0.120	0.315	0.196	2.33	1.30	4310.0	120	0.31	0.97	0.18	24.30	11.55	182.5	55
C385617		1.44	0.356	0.464	0.296	4.12	1.07	4390.0	80	0.07	0.74	0.02	<0.02	11.00	37.4	47
C385618		0.68	0.001	<0.005	<0.001	0.02	0.02	<5	250	<0.05	<0.01	31.70	1.83	0.12	0.8	<1
C385619		0.46	0.027	0.033	0.025	4.79	3.25	891.0	320	1.63	0.29	3.99	37.50	69.70	8.9	182
C385620		0.28	0.018	0.033	0.028	4.47	2.05	876.0	210	1.19	0.17	9.20	80.90	52.30	14.3	191
C385621		0.34	0.003	0.010	0.004	0.29	0.24	38	1330	0.21	0.01	13.50	4.30	11.65	2.0	29
C385622		0.28	0.004	0.011	0.004	0.74	0.63	119	1030	0.63	0.03	34.70	13.00	40.40	6.3	36
C385623		0.34	0.021	0.076	0.037	4.81	2.47	1520	70	0.83	0.15	19.85	43.00	122.00	39.2	102
C385624		0.36	0.256	0.449	0.296	3.60	2.83	56.0	410	1.12	0.81	0.15	1.63	128.50	1.5	73
C385625		1.12	0.007	0.011	0.003	0.82	8.53	47.8	620	3.73	0.32	0.05	0.47	63.30	1.0	120
C385626		0.06	0.468	0.638	0.391	3.96	2.52	131.0	150	0.74	0.57	0.10	1.81	54.10	6.7	74
C385627		1.66	0.002	0.010	<0.001	0.27	0.33	12	4340	0.23	<0.01	17.65	9.35	4.57	1.5	10
C385628		0.38	0.017	<0.005	0.012	14.25	2.59	89.8	460	1.47	0.84	6.41	2.25	105.50	29.5	113
C385629		0.26	0.001	<0.005	0.006	6.04	2.86	90.7	440	1.40	0.43	4.55	2.79	87.30	50.3	90
C385630		0.26	0.015	0.015	0.019	11.20	2.61	161.5	410	1.80	0.71	4.78	3.68	37.10	5.0	202
C385631		0.36	0.002	<0.005	0.004	0.04	0.07	0.9	160	<0.05	<0.01	0.06	<0.02	0.52	0.8	2
C385632		0.18	0.032	0.044	0.037	1.60	4.85	438.0	340	1.73	0.30	0.56	12.15	79.20	50.3	102
C385633		0.48	0.047	0.162	0.100	6.31	1.45	2880	370	0.80	0.54	10.10	67.10	44.90	116.5	53

Comments: Interference: Ca>10% on ICP-MS As,ICP-AES results shown. Mo>400ppm on ICP-MS Cd,ICP-AES results shown. Detection limits on samples requiring dilutions for Hg-CV41 have been increased according to the dilution factor.

ALS Chemex

EXCELLENCE IN ANALYTICAL CHEMISTRY

ALS Canada Ltd.

212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: STRATEGIC METALS LTD.
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO

Finalized Date: 30-JUN-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07060911

Sample Description	Method	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	Hg-CV41	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61
	Analyte	Cs	Cu	Fe	Ga	Ge	Hf	Hg	In	K	La	Li	Mg	Mn	Mo	Na
	Units	ppm	ppm	%	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	%	ppm	ppm	%
	LOR	0.05	0.2	0.01	0.05	0.05	0.1	0.01	0.005	0.01	0.5	0.2	0.01	5	0.05	0.01
C385601		1.19	231.0	20.40	14.30	9.47	0.3	1.00	0.261	0.44	32.9	6.7	0.03	101	2190.00	0.03
C385602		13.70	37.1	2.71	28.80	0.32	2.2	0.13	0.035	2.95	19.5	24.3	0.58	94	56.20	0.06
C385603		1.48	127.5	19.45	5.98	9.70	0.4	0.5	0.025	0.57	24.3	6.9	0.04	94	2350.00	0.03
C385604		12.40	19.5	2.18	22.90	0.36	1.9	0.08	0.031	2.26	11.7	21.4	0.46	28	75.60	0.05
C385605		1.31	205.0	22.70	8.75	7.54	0.3	1	0.154	0.41	12.1	6.0	0.03	139	2760.00	0.03
C385606		9.10	38.1	2.64	18.90	0.27	1.4	0.08	0.027	1.73	0.7	16.8	0.35	75	41.20	0.04
C385607		0.86	129.0	23.70	4.38	7.89	0.2	1	<0.005	0.29	5.9	6.0	0.01	102	2820.00	0.02
C385608		13.10	16.5	1.46	26.80	0.33	2.1	0.11	0.028	2.63	22.4	20.8	0.51	29	72.40	0.06
C385609		2.83	140.5	17.80	7.34	7.02	0.5	0.5	<0.005	0.77	7.3	8.3	0.10	86	2160.00	0.03
C385610		12.55	21.0	1.92	25.70	0.45	1.9	0.12	0.029	2.78	24.7	19.1	0.55	40	138.50	0.06
C385611		1.63	141.5	22.70	7.34	7.13	0.4	0.4	0.085	0.43	9.3	6.3	0.04	126	2420.00	0.02
C385612		15.65	25.3	1.96	29.90	0.35	2.4	0.12	0.030	2.91	26.5	24.5	0.57	58	76.10	0.06
C385613		6.37	8.4	0.89	19.35	0.65	1.7	1.02	0.022	1.66	61.7	12.1	0.38	25	168.50	0.04
C385614		1.28	387.0	6.25	6.68	0.69	0.5	0.05	0.118	0.27	14.9	4.6	0.16	910	180.00	0.01
C385615		3.98	97.4	1.63	14.60	1.14	1.4	0.74	0.037	0.91	14.6	10.2	0.24	53	145.50	0.03
C385616		1.72	372.0	20.50	11.10	8.78	0.5	2	0.240	0.39	4.8	3.5	0.07	129	2380.00	0.03
C385617		1.36	89.9	17.00	5.41	16.50	0.4	0.8	<0.005	0.31	5.4	3.5	0.06	93	2530.00	0.02
C385618		<0.05	1.1	0.02	0.12	0.16	<0.1	<0.01	<0.005	0.01	<0.5	<0.2	0.02	16	2.51	0.01
C385619		4.37	196.0	2.65	12.45	1.03	1.7	1.30	0.051	1.14	64.2	18.7	0.27	46	374.00	0.13
C385620		2.91	284.0	2.30	7.47	1.43	1.1	1.08	0.027	0.74	64.4	10.8	0.37	52	410.00	0.05
C385621		0.35	17.7	0.82	1.25	0.21	0.2	0.29	<0.005	0.07	23.3	1.2	0.26	79	28.60	0.02
C385622		0.63	50.3	0.59	3.71	0.40	0.2	0.65	<0.005	0.22	71.1	3.0	0.63	75	80.60	0.03
C385623		2.32	353.0	3.24	11.40	2.49	1.0	2.75	<0.005	0.92	104.8	13.9	0.73	95	783.00	0.12
C385624		3.59	11.4	0.96	11.95	1.20	1.1	0.88	0.018	0.87	93.6	9.6	0.20	44	112.00	0.03
C385625		12.55	9.7	1.82	33.60	0.43	3.1	0.30	0.084	2.86	44.9	18.3	0.62	17	161.50	0.09
C385626		3.00	29.5	4.12	10.05	1.31	1.2	0.79	0.033	0.91	27.0	14.4	0.19	179	349.00	0.04
C385627		0.13	12.1	0.18	0.75	0.07	0.2	0.04	<0.005	0.08	4.2	1.1	11.40	439	16.85	0.03
C385628		2.26	43.9	2.48	5.90	0.28	1.4	0.79	0.011	0.98	46.9	6.2	0.17	92	22.60	0.18
C385629		2.27	46.7	2.86	5.73	0.27	1.3	0.38	0.011	1.02	41.5	6.2	0.16	103	23.70	0.21
C385630		2.62	124.5	4.06	6.66	0.45	1.4	0.66	0.016	0.94	21.7	7.8	0.25	39	48.40	0.13
C385631		0.08	1.1	0.21	1.87	0.05	<0.1	0.01	<0.005	0.01	<0.5	0.6	0.01	<5	36.80	2.88
C385632		6.74	86.1	7.70	12.70	1.09	2.0	0.33	0.030	1.65	51.7	39.4	0.37	410	484.00	0.06
C385633		1.28	401.0	8.83	8.06	4.50	0.7	0.33	0.082	0.47	36.8	7.0	0.49	66	1420.00	0.03

Comments: Interference: Ca>10% on ICP-MS As,ICP-AES results shown. Mo>400ppm on ICP-MS Cd,ICP-AES results shown. Detection limits on samples requiring dilutions for Hg-CV41 have been increased according to the dilution factor.

ALS Chemex

EXCELLENCE IN ANALYTICAL CHEMISTRY

ALS Canada Ltd.

212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: STRATEGIC METALS LTD.
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO

Finalized Date: 30-JUN-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07060911

Sample Description	Method	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61
	Analyte	Nb	Ni	P	Pb	Rb	Re	S	Sb	Sc	Se	Sn	Sr	Ta	Te	Th
	Units	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm
	LOR	0.1	0.2	10	0.5	0.1	0.002	0.01	0.05	0.1	1	0.2	0.2	0.05	0.05	0.2
C385601		1.4	>10000	4560	30.6	18.8	37.000	>10.0	164.50	3.6	>1000	7.9	169.5	<0.05	23.40	1.5
C385602		10.5	186.0	310	17.2	176.0	0.144	2.94	24.60	13.2	68	2.5	190.5	0.75	0.20	6.5
C385603		1.9	>10000	1260	36.0	23.7	41.500	>10.0	160.50	3.1	>1000	3.8	84.2	<0.05	15.95	0.9
C385604		9.0	508.0	260	13.0	138.0	0.623	1.09	23.20	11.3	80	2.1	413.0	0.63	0.46	3.9
C385605		1.4	>10000	1820	22.2	18.0	34.200	>10.0	181.00	2.6	>1000	6.8	105.5	<0.05	19.20	0.8
C385606		6.7	203.0	270	11.4	109.0	0.139	2.71	19.45	8.9	60	1.5	173.0	0.47	0.22	1.2
C385607		0.9	>10000	1450	22.8	12.8	39.200	>10.0	184.00	1.6	>1000	4.3	98.1	<0.05	16.35	0.6
C385608		10.4	144.0	170	14.4	160.0	0.319	1.24	32.70	12.4	75	2.7	87.4	0.69	0.40	4.3
C385609		2.6	>10000	310	26.2	39.1	30.200	>10.0	159.50	3.3	>1000	2.6	79.2	<0.05	12.85	0.8
C385610		9.5	1045.0	300	14.3	154.5	1.100	1.84	33.30	11.2	106	2.6	64.3	0.65	0.82	4.2
C385611		1.6	>10000	1010	20.1	21.9	35.500	>10.0	172.00	2.6	>1000	5.1	45.5	<0.05	15.65	1.0
C385612		11.4	273.0	270	18.1	187.0	0.336	2.02	29.60	12.8	83	2.8	60.7	0.80	0.36	4.6
C385613		8.1	124.5	510	52.9	92.4	31.800	0.56	75.80	9.7	162	2.0	207.0	0.55	1.48	5.2
C385614		2.1	5260.0	2800	3.0	19.7	1.140	7.86	6.35	10.2	83	0.6	400.0	0.14	0.41	2.9
C385615		5.5	375.0	560	42.5	63.4	43.000	2.30	74.70	7.6	314	1.3	171.5	0.39	0.57	3.0
C385616		1.8	>10000	940	49.2	26.2	38.400	>10.0	156.00	3.3	>1000	5.6	49.4	<0.05	24.90	2.3
C385617		1.8	>10000	50	68.3	21.0	>50	>10.0	166.00	1.6	>1000	1.8	72.1	<0.05	9.88	1.0
C385618		0.1	63.1	10	1.2	0.1	0.041	8.26	1.75	0.2	3	<0.2	2000.0	<0.05	0.05	<0.2
C385619		5.9	1010.0	7480	28.2	68.7	3.700	2.66	122.50	7.6	225	1.8	302.0	0.51	1.00	5.2
C385620		3.4	4350.0	4420	26.2	42.6	4.210	3.84	163.00	7.4	358	0.8	450.0	0.24	1.13	2.9
C385621		0.8	457.0	1580	2.9	3.6	0.641	0.40	7.37	1.7	44	0.2	901.0	<0.05	0.09	0.4
C385622		1.1	1585.0	6290	6.6	11.8	0.900	1.31	23.10	3.4	70	0.2	1430.0	0.05	0.19	1.0
C385623		3.1	7410.0	>10000	30.5	43.6	7.720	5.07	265.00	5.2	565	2.7	1090.0	0.11	1.11	3.4
C385624		5.4	198.0	530	60.1	55.8	>50	0.81	80.20	8.9	300	1.1	346.0	0.39	0.67	4.0
C385625		12.8	62.1	320	22.8	182.5	0.692	1.08	32.90	14.7	92	3.1	220.0	0.94	1.79	7.3
C385626		4.0	679.0	440	63.5	53.0	>50	2.22	82.80	5.3	361	1.9	274.0	0.27	1.64	3.6
C385627		0.6	46.6	370	1.8	2.9	0.038	0.15	3.15	1.4	5	<0.2	1635.0	<0.05	<0.05	0.4
C385628		5.7	64.4	270	67.5	52.2	0.035	7.23	91.00	6.0	40	0.6	710.0	0.34	1.31	3.4
C385629		6.4	123.0	260	44.7	56.6	0.039	5.18	41.60	6.2	38	0.6	644.0	0.35	0.70	3.9
C385630		5.0	89.3	1560	68.0	54.9	0.075	5.66	95.90	9.1	88	0.8	710.0	0.35	1.10	3.3
C385631		0.1	719.0	30	0.5	1.0	0.002	2.40	0.41	0.6	<1	<0.2	9.9	<0.05	<0.05	0.2
C385632		8.7	5880.0	300	35.3	103.5	3.880	>10.0	43.20	8.8	203	1.7	114.0	0.56	0.90	5.2
C385633		2.6	>10000	810	59.6	24.0	10.200	>10.0	126.00	5.0	>1000	3.8	388.0	0.15	4.04	1.9

Comments: Interference: Ca>10% on ICP-MS As,ICP-AES results shown. Mo>400ppm on ICP-MS Cd,ICP-AES results shown. Detection limits on samples requiring dilutions for Hg-CV41 have been increased according to the dilution factor.

ALS Chemex

EXCELLENCE IN ANALYTICAL CHEMISTRY

ALS Canada Ltd.

212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: STRATEGIC METALS LTD.
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO

Finalized Date: 30-JUN-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07060911

Sample Description	Method	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	ME-MS61	Ni-AA62	Zn-AA62
	Analyte	Ti	Tl	U	V	W	Y	Zn	Zr	Ni	Zn
	Units	%	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%	%
	LOR	0.005	0.02	0.1	1	0.1	0.1	2	0.5	0.01	0.01
C385601		0.034	340.00	66.6	185	1.3	64.1	>10000	14.6	4.89	1.40
C385602		0.341	11.65	7.7	1375	1.3	16.7	121	80.1		
C385603		0.046	268.00	21.5	240	1.6	44.8	954	16.0	3.73	
C385604		0.267	13.50	7.1	1075	1.1	15.3	181	68.1		
C385605		0.035	280.00	40.9	196	1.7	40.9	6710	14.1	3.61	
C385606		0.205	8.69	8.3	850	0.8	14.3	246	52.0		
C385607		0.021	295.00	10.5	128	1.7	27.6	2320	8.0	3.32	
C385608		0.308	20.80	6.8	1220	1.2	15.3	130	78.9		
C385609		0.075	256.00	5.9	363	1.7	16.6	361	20.7	3.20	
C385610		0.329	27.20	6.2	1345	1.2	13.9	36	74.1		
C385611		0.040	281.00	18.4	190	1.8	19.8	4100	14.8	3.46	
C385612		0.344	15.10	7.3	1390	1.5	15.0	57	86.3		
C385613		0.288	25.80	9.5	1240	1.4	10.9	38	73.2		
C385614		0.049	11.60	50.5	207	0.5	135.5	6540	24.0		
C385615		0.158	28.20	18.8	727	1.3	27.6	258	66.0		
C385616		0.055	257.00	26.9	374	1.5	22.4	6170	27.2	4.78	
C385617		0.056	248.00	5.4	319	2.2	6.4	189	18.4	1.29	
C385618		<0.005	0.32	27.9	2	<0.1	0.1	387	0.9		
C385619		0.157	14.50	124.0	2540	1.4	120.0	2930	70.5		
C385620		0.099	20.30	73.1	2600	1.1	95.2	5340	57.1		
C385621		0.011	2.14	20.0	241	0.1	33.5	637	15.1		
C385622		0.028	4.48	64.1	552	0.3	119.5	2130	31.6		
C385623		0.090	36.10	193.5	1255	1.7	256.0	4500	54.9		
C385624		0.144	14.90	15.7	582	1.2	62.8	181	45.1		
C385625		0.400	52.60	10.2	2040	1.6	14.5	27	114.0		
C385626		0.105	62.70	9.1	541	1.1	50.0	193	48.7		
C385627		0.015	0.49	4.0	379	0.1	11.3	360	14.4		
C385628		0.156	14.30	7.4	1460	0.7	33.2	137	57.6		
C385629		0.160	5.92	6.9	1230	0.9	29.9	221	51.3		
C385630		0.138	13.20	18.3	2060	1.3	25.4	283	58.0		
C385631		<0.005	<0.02	0.2	2410	0.1	0.3	<2	2.1		
C385632		0.248	39.40	14.5	1470	1.6	41.7	1030	64.9		
C385633		0.058	161.50	43.2	544	1.5	84.1	9680	26.1	3.54	

Comments: Interference: Ca>10% on ICP-MS As,ICP-AES results shown. Mo>400ppm on ICP-MS Cd,ICP-AES results shown. Detection limits on samples requiring dilutions for Hg-CV41 have been increased according to the dilution factor.

ALS Chemex
EXCELLENCE IN ANALYTICAL CHEMISTRY
ALS Canada Ltd.
212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: **STRATEGIC METALS LTD.**
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Finalized Date: 25-JUN-2007
Account: MTT

CERTIFICATE VA07060639

Project: NIMO

P.O. No.:

This report is for 185 Soil samples submitted to our lab in Vancouver, BC, Canada on 18-JUN-2007.

The following have access to data associated with this certificate:

JOAN MARIACHER

SAMPLE PREPARATION

ALS CODE	DESCRIPTION
WEI-21	Received Sample Weight
DRY-22	Drying - Maximum Temp 60C
LOG-22	Sample login - Rcd w/o BarCode
SCR-41	Screen to -180um and save both

ANALYTICAL PROCEDURES

ALS CODE	DESCRIPTION
ME-MS41	51 anal. aqua regia ICPMS

To: **STRATEGIC METALS LTD.**
ATTN: JOAN MARIACHER
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

is the Final Report and supersedes any preliminary report with this certificate number. Results apply to samples as submitted. All es of this report have been checked and approved for release.

Signature: Lawrence Ng

Lawrence Ng, Laboratory Manager - Vancouver

ALS Chemex

EXCELLENCE IN ANALYTICAL CHEMISTRY

ALS Canada Ltd.

212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: STRATEGIC METALS LTD.
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO

Finalized Date: 25-JUN-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07060639

Sample Description	Method	WEI-21	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41
	Analyte	Recvd Wt.	Ag	Al	As	Au	B	Ba	Be	Bi	Ca	Cd	Ce	Co	Cr	Cs
	Units	kg	ppm	%	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppm	ppm	ppm
	LOR	0.02	0.01	0.01	0.1	0.2	10	10	0.05	0.01	0.01	0.01	0.02	0.1	1	0.05
CC20201		0.20	0.19	2.38	14.8	<0.2	<10	300	0.49	0.21	0.06	0.22	21.60	8.6	34	1.27
CC20202		0.22	0.41	2.09	21.9	<0.2	<10	380	0.57	0.22	0.06	0.34	23.50	7.8	38	1.57
CC20203		0.20	0.37	1.79	26.3	<0.2	<10	340	0.45	0.25	0.07	0.34	21.60	5.8	35	1.13
CC20204		0.26	0.39	1.05	11.4	<0.2	<10	220	0.26	0.19	0.04	0.30	20.40	3.5	19	0.80
CC20205		0.14	0.29	1.74	20.4	<0.2	<10	230	0.33	0.30	0.05	0.26	17.15	4.2	28	1.11
CC20206		0.08	0.32	0.66	9.5	<0.2	<10	670	0.21	0.11	0.25	0.22	11.05	1.4	14	0.74
CC20207		0.12	0.27	0.74	29.5	<0.2	<10	360	0.20	0.18	0.36	0.66	12.75	4.6	22	0.62
CC20208		0.16	0.19	1.33	44.6	<0.2	<10	280	0.33	0.20	0.04	0.61	13.55	5.0	27	0.77
CC20209		0.08	0.53	0.70	9.2	<0.2	<10	610	0.22	0.17	0.19	1.56	13.70	2.1	13	0.51
CC20210		0.12	1.67	1.11	36.5	<0.2	<10	420	0.27	0.27	0.03	0.43	14.10	2.3	36	1.09
CC20211		0.14	1.54	0.86	64.6	<0.2	<10	480	0.23	0.30	0.02	0.67	14.35	2.0	33	0.85
CC20212		Not Recvd														
CC20213		Not Recvd														
CC20214		Not Recvd														
CC20215		Not Recvd														
CC20216		Not Recvd														
CC20217		Not Recvd														
CC20218		Not Recvd														
CC20219		Not Recvd														
CC20220		0.18	1.62	1.53	15.8	<0.2	<10	330	0.37	0.22	0.04	0.36	18.90	4.3	26	0.98
CC20227		0.12	0.57	0.82	76.6	<0.2	<10	290	0.13	0.28	0.03	0.08	17.80	2.0	22	1.18
CC20228		0.16	0.21	1.28	38.5	<0.2	<10	280	0.16	0.24	0.05	0.08	18.25	3.1	29	1.27
CC20229		0.16	0.48	1.37	86.9	<0.2	<10	450	0.24	0.24	0.05	0.08	16.15	1.8	61	1.60
CC20230		0.14	0.82	0.41	33.9	<0.2	<10	460	0.09	0.23	0.02	<0.01	15.85	1.2	13	1.00
CC20231		0.20	2.41	1.25	59.3	<0.2	<10	770	0.31	0.25	0.07	0.17	17.65	1.7	59	1.86
CC20232		0.12	0.44	1.00	23.9	<0.2	<10	230	0.20	0.27	0.03	0.05	20.20	2.7	22	0.91
CC20233		0.14	0.94	1.13	82.9	<0.2	<10	750	0.29	0.23	0.04	0.72	15.60	2.2	31	1.42
CC20234		0.14	1.09	0.93	54.7	<0.2	<10	930	0.31	0.24	0.05	2.50	15.60	1.5	23	1.32
CC20235		0.28	0.83	0.71	14.1	<0.2	<10	710	0.25	0.13	0.05	0.93	17.95	2.4	16	0.71
CC20236		0.20	0.54	0.56	16.3	<0.2	<10	540	0.17	0.13	0.06	0.84	16.10	1.1	14	0.70
CC20237		0.12	0.47	0.91	6.1	<0.2	<10	1050	0.33	0.13	1.03	1.01	24.00	10.5	15	0.49
CC20238		0.12	0.89	0.89	6.5	<0.2	<10	2860	0.35	0.12	0.88	1.02	21.20	6.0	15	0.50
CC20239		0.14	0.97	0.94	6.2	<0.2	<10	3920	0.45	0.11	1.66	1.19	25.50	7.0	17	0.50
CC20240		0.12	0.69	1.30	7.2	<0.2	<10	4450	0.66	0.16	0.77	0.40	36.50	9.0	22	0.58
CC20241		0.24	0.57	0.97	14.8	<0.2	10	3440	0.66	0.07	9.25	6.42	28.30	6.9	30	1.41
CC20242		0.28	0.46	0.75	9	<0.2	10	1740	0.51	0.07	11.50	2.27	24.50	7.3	20	1.65
CC20246		0.18	0.57	0.65	9.4	<0.2	10	2070	0.45	0.11	3.09	1.87	21.60	6.5	15	0.98
CC20247		0.12	0.70	0.54	11.2	<0.2	10	1240	0.35	0.11	4.84	2.69	22.10	7.6	16	1.05
CC20248		0.18	0.65	0.67	15.0	<0.2	10	1030	0.38	0.11	4.63	3.37	22.60	9.7	14	1.06
CC20249		0.20	0.62	0.61	14.8	<0.2	10	4040	0.25	0.15	2.56	1.96	10.55	11.8	13	1.24

Comments: Interference: Ca>10% on ICP-MS As,ICP-AES results shown. Gold determinations by ME-MS41 are semi-quantitative due to the small sample weight used (0.5g). NSS is non-sufficient sample.

ALS Chemex
EXCELLENCE IN ANALYTICAL CHEMISTRY
ALS Canada Ltd.
212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: STRATEGIC METALS LTD.
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO

Finalized Date: 25-JUN-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07060639

Sample Description	Method	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41
	Analyte	Cu	Fe	Ga	Ge	Hf	Hg	In	K	La	Li	Mg	Mn	Mo	Na	Nb
	Units	ppm	%	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	%	ppm	ppm	%	ppm
	LOR	0.2	0.01	0.05	0.05	0.02	0.01	0.005	0.01	0.2	0.1	0.01	5	0.05	0.01	0.05
CC20201		17.6	3.04	5.97	<0.05	0.09	0.02	0.037	0.06	11.3	21.4	0.40	204	7.99	0.01	1.10
CC20202		23.3	3.15	5.88	0.05	0.09	0.03	0.038	0.08	12.7	21.2	0.37	180	13.15	0.01	0.72
CC20203		20.2	3.26	6.07	0.05	0.05	0.02	0.035	0.09	11.6	13.8	0.32	176	22.60	0.01	0.89
CC20204		10.6	2.05	4.37	<0.05	0.03	0.01	0.018	0.04	11.0	8.1	0.13	107	13.40	<0.01	0.73
CC20205		14.9	3.55	6.51	0.09	0.04	0.03	0.041	0.09	8.9	15.6	0.20	124	25.20	0.01	1.05
CC20206		12.3	0.94	2.90	0.05	0.03	0.11	0.018	0.04	5.8	3.8	0.09	29	6.92	0.01	0.31
CC20207		23.6	2.42	3.47	0.09	0.04	0.10	0.028	0.12	6.6	5.5	0.16	111	37.70	0.01	0.49
CC20208		26.3	3.76	4.83	0.12	0.05	0.03	0.035	0.10	7.2	11.2	0.21	93	69.60	0.01	0.74
CC20209		23.1	1.61	4.31	0.06	<0.02	0.06	0.017	0.05	7.2	0.9	0.05	48	16.65	0.01	0.42
CC20210		25.3	3.53	5.66	0.12	0.02	0.03	0.040	0.16	9.4	7.6	0.12	75	53.80	0.01	0.72
CC20211		27.1	4.09	5.80	0.16	0.02	0.04	0.055	0.25	8.2	3.0	0.07	52	143.50	0.02	0.65
CC20212																
CC20213																
CC20214																
CC20215																
CC20216																
CC20217																
CC20218																
CC20219																
CC20220		18.8	2.92	5.63	0.09	0.03	0.02	0.030	0.08	10.0	13.2	0.21	131	22.70	0.01	0.93
CC20227		14.1	2.90	6.35	0.09	0.03	0.08	0.024	0.07	9.3	2.3	0.09	94	98.00	0.01	0.94
CC20228		11.3	3.18	6.62	0.09	0.02	0.09	0.025	0.06	9.3	5.6	0.18	154	39.70	0.01	1.19
CC20229		15.5	3.74	5.49	0.12	0.03	0.36	0.063	0.08	8.8	3.2	0.13	79	77.80	0.02	0.48
CC20230		9.3	1.67	4.61	0.12	<0.02	0.09	0.016	0.08	8.4	0.8	0.03	34	85.80	0.01	0.50
CC20231		19.3	3.29	5.13	0.16	0.07	0.56	0.097	0.11	10.2	5.0	0.11	80	84.70	0.01	0.25
CC20232		14.1	3.08	6.96	0.09	0.02	0.10	0.028	0.06	10.7	2.9	0.09	97	35.20	0.01	1.13
CC20233		171.0	4.08	3.58	0.20	0.03	0.53	0.057	0.17	9.1	2.1	0.08	66	125.50	0.02	0.43
CC20234		77.1	3.17	3.35	0.22	0.03	0.87	0.049	0.16	9.5	2.0	0.07	31	115.00	0.01	0.32
CC20235		29.3	1.48	2.73	0.09	0.02	0.37	0.029	0.08	9.7	3.8	0.13	75	37.00	0.01	0.33
CC20236		21.7	1.09	2.41	0.10	0.02	0.27	0.022	0.07	8.8	2.4	0.09	26	33.80	0.01	0.29
CC20237		17.9	2.36	2.55	0.08	0.06	0.14	0.021	0.06	12.1	7.2	0.27	563	2.46	0.02	0.28
CC20238		31.4	1.93	2.36	0.08	0.08	0.17	0.025	0.07	11.1	5.0	0.22	246	3.37	0.02	0.28
CC20239		31.6	2.47	2.43	0.09	0.07	0.13	0.027	0.07	13.8	4.5	0.30	319	3.56	0.02	0.29
CC20240		26.1	3.09	3.31	0.12	0.09	0.10	0.032	0.09	19.0	7.0	0.27	267	3.36	0.02	0.37
CC20241		48.3	1.85	3.22	0.11	0.08	0.13	0.026	0.18	16.2	12.8	2.23	216	20.20	0.03	0.24
CC20242		41.1	1.89	2.38	0.10	0.12	0.10	0.025	0.14	13.4	13.4	1.79	209	12.65	0.03	0.14
CC20246		44.1	1.91	1.81	0.08	0.08	0.13	0.028	0.14	12.1	6.2	0.98	183	4.49	0.02	0.17
CC20247		46.3	2.38	1.24	0.09	0.20	0.14	0.029	0.16	11.4	2.8	2.20	264	8.57	0.03	0.09
CC20248		60.7	2.73	1.57	0.11	0.12	0.17	0.033	0.15	11.9	4.3	1.84	266	13.05	0.03	0.13
CC20249		68.4	3.08	0.99	0.10	0.30	0.27	0.042	0.20	4.9	1.1	1.27	233	7.22	0.03	0.05

Comments: Interference: Ca>10% on ICP-MS As,ICP-AES results shown. Gold determinations by ME-MS41 are semi-quantitative due to the small sample weight used (0.5g). NSS is non-sufficient sample.

ALS Chemex

EXCELLENCE IN ANALYTICAL CHEMISTRY

ALS Canada Ltd.

212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: STRATEGIC METALS LTD.
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO

Finalized Date: 25-JUN-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07060639

Sample Description	Method	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41
	Analyte	Ni	P	Pb	Rb	Re	S	Sb	Sc	Se	Sn	Sr	Ta	Te	Th	Ti
	Units	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%
	LOR	0.2	10	0.2	0.1	0.001	0.01	0.05	0.1	0.2	0.2	0.2	0.01	0.01	0.2	0.005
CC20201		25.2	240	12.0	11.0	<0.001	0.02	1.44	3.7	2.7	0.7	10.8	<0.01	0.07	3.9	0.026
CC20202		22.2	320	13.5	17.3	<0.001	0.04	5.80	4.2	3.3	0.7	17.3	<0.01	0.07	4.2	0.022
CC20203		19.4	390	12.9	14.4	<0.001	0.06	8.50	3.7	4.0	0.7	19.1	<0.01	0.11	3.3	0.018
CC20204		10.7	210	11.3	9.3	<0.001	0.03	2.26	1.9	2.4	0.6	11.4	<0.01	0.06	2.6	0.018
CC20205		14.9	450	12.9	15.3	<0.001	0.07	2.42	2.3	2.7	0.7	12.8	0.01	0.13	2.4	0.016
CC20206		8.6	420	7.4	6.9	0.004	0.07	1.45	2.1	4.0	0.4	23.1	0.02	0.08	1.3	0.007
CC20207		58.3	430	12.5	11.4	0.001	0.22	4.54	2.4	7.1	0.5	39.5	0.01	0.14	1.9	0.011
CC20208		65.1	320	13.9	10.7	<0.001	0.18	6.41	2.3	11.3	0.7	24.8	<0.01	0.20	2.3	0.011
CC20209		14.2	530	10.7	3.4	<0.001	0.05	1.64	0.6	3.1	0.7	13.1	0.01	0.08	<0.2	0.015
CC20210		12.4	870	22.5	12.1	<0.001	0.36	10.60	2.0	11.5	0.8	36.4	<0.01	0.25	1.3	0.014
CC20211		17.4	940	21.1	15.3	<0.001	0.64	16.40	2.2	21.4	0.9	76.0	<0.01	0.33	2.1	0.015
CC20212																
CC20213																
CC20214																
CC20215																
CC20216																
CC20217																
CC20218																
CC20219																
CC20220		12.1	400	11.9	11.5	<0.001	0.12	3.95	2.4	7.2	0.7	14.9	<0.01	0.11	2.4	0.018
CC20227		14.0	1060	16.7	11.6	0.001	0.10	12.45	1.5	7.9	1.1	27.6	<0.01	0.18	1.5	0.023
CC20228		11.1	580	11.9	9.2	<0.001	0.05	5.44	1.7	4.8	0.8	21.4	<0.01	0.12	1.1	0.026
CC20229		11.2	4450	17.0	11.0	0.002	0.10	9.86	2.4	11.2	0.8	19.5	<0.01	0.17	0.7	0.012
CC20230		4.6	460	19.3	8.3	0.001	0.12	15.15	1.5	19.6	1.0	14.8	<0.01	0.29	1.2	0.016
CC20231		8.7	4680	20.8	13.5	0.004	0.16	23.40	1.7	21.3	1.1	38.7	<0.01	0.43	0.6	0.008
CC20232		9.0	510	13.1	10.6	0.001	0.05	8.08	1.6	6.1	0.9	11.1	<0.01	0.16	1.8	0.029
CC20233		37.8	1620	16.5	15.3	0.025	0.46	19.30	2.4	31.1	0.9	37.0	<0.01	0.31	1.5	0.010
CC20234		39.5	950	18.7	13.9	0.019	0.40	18.50	2.7	37.1	1.1	66.5	<0.01	0.31	2.0	0.007
CC20235		19.2	450	10.6	8.1	0.002	0.08	8.65	2.1	10.0	0.5	28.0	<0.01	0.17	1.5	0.013
CC20236		15.6	420	11.2	8.5	0.012	0.04	7.92	1.7	14.6	0.5	31.5	<0.01	0.14	1.6	0.009
CC20237		18.5	670	9.5	9.1	0.006	0.11	0.95	2.4	2.6	0.3	41.6	<0.01	0.04	2.2	0.007
CC20238		23.1	740	9.8	7.2	0.008	0.09	1.14	2.9	3.3	0.3	57.8	<0.01	0.05	1.8	0.006
CC20239		31.6	910	10.9	6.9	0.002	0.09	1.13	2.8	3.4	0.3	91.1	0.01	0.06	1.4	0.007
CC20240		30.5	700	11.1	9.3	0.002	0.05	0.86	3.6	3.0	0.3	61.2	<0.01	0.05	3.0	0.007
CC20241		72.2	2180	9.1	14.0	0.016	0.13	4.57	3.6	4.4	0.5	418.0	<0.01	0.07	3.2	0.008
CC20242		42.6	1530	10.5	10.9	0.010	0.18	2.81	3.5	3.2	0.3	577.0	<0.01	0.06	3.8	<0.005
CC20246		33.2	1940	17.6	9.3	0.008	0.18	2.17	3.0	2.9	0.2	107.0	<0.01	0.07	3.4	0.006
CC20247		42.7	960	9.3	7.9	0.026	0.33	3.82	4.5	3.8	0.3	190.5	<0.01	0.06	4.5	<0.005
CC20248		89.0	1260	10.0	8.7	0.025	0.39	3.39	3.9	5.7	0.3	178.5	0.01	0.09	3.7	<0.005
CC20249		78.7	650	8.8	10.1	0.008	0.15	2.81	6.1	3.9	0.3	153.5	<0.01	0.06	4.4	<0.005

Comments: Interference: Ca>10% on ICP-MS As,ICP-AES results shown. Gold determinations by ME-MS41 are semi-quantitative due to the small sample weight used (0.5g). NSS is non-sufficient sample.

ALS Chemex
EXCELLENCE IN ANALYTICAL CHEMISTRY
ALS Canada Ltd.
212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: STRATEGIC METALS LTD.
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO

CERTIFICATE OF ANALYSIS VA07060639

Sample Description	Method	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41
	Analyte	Tl	U	V	W	Y	Zn	Zr
	Units	ppm	ppm	ppm	ppm	ppm	ppm	ppm
	LOR	0.02	0.05	1	0.05	0.05	2	0.5
CC20201		0.38	0.69	95	0.16	2.62	84	3.2
CC20202		0.59	1.21	204	0.15	3.49	74	3.3
CC20203		0.79	1.40	316	0.18	3.06	75	1.9
CC20204		0.57	0.62	139	0.13	1.78	52	1.3
CC20205		1.26	0.66	201	0.37	2.14	75	1.1
CC20206		0.82	1.10	75	0.22	2.76	30	0.6
CC20207		2.21	1.43	215	0.22	3.38	191	1.1
CC20208		3.63	1.22	289	0.23	3.58	141	1.8
CC20209		0.40	1.05	120	0.20	2.31	55	<0.5
CC20210		2.35	1.79	357	0.32	3.07	88	<0.5
CC20211		6.15	2.88	666	0.39	4.16	121	0.7
CC20212								
CC20213								
CC20214								
CC20215								
CC20216								
CC20217								
CC20218								
CC20219								
CC20220		1.03	0.87	167	0.19	2.65	63	1.1
CC20227		2.97	2.14	423	0.43	4.51	31	0.6
CC20228		1.13	1.11	310	0.29	3.39	43	<0.5
CC20229		2.48	11.40	451	0.37	6.41	28	0.7
CC20230		2.12	1.31	308	0.34	2.87	18	<0.5
CC20231		4.27	19.45	427	0.46	9.07	26	1.6
CC20232		1.00	1.45	331	0.26	2.45	38	0.5
CC20233		5.23	7.40	570	0.38	6.57	97	0.9
CC20234		4.79	7.40	380	0.38	8.07	112	0.9
CC20235		1.86	2.99	151	0.18	6.27	67	0.5
CC20236		1.61	2.28	154	0.15	5.04	47	0.5
CC20237		0.15	1.21	63	0.09	9.58	106	1.4
CC20238		0.12	1.82	45	0.06	11.15	93	2.0
CC20239		0.10	2.94	66	0.09	15.65	105	1.6
CC20240		0.10	2.47	74	0.11	21.70	103	1.8
CC20241		0.53	4.61	242	0.13	20.60	563	3.4
CC20242		0.23	3.57	109	0.08	15.85	231	6.2
CC20246		0.14	2.38	66	0.10	15.05	286	3.0
CC20247		0.14	2.90	75	0.07	15.65	329	11.0
CC20248		0.53	3.75	69	0.08	17.30	408	4.9
CC20249		0.12	2.99	35	0.05	17.55	279	12.0

Comments: Interference: Ca>10% on ICP-MS As,ICP-AES results shown. Gold determinations by ME-MS41 are semi-quantitative due to the small sample weight used (0.5g). NSS is non-sufficient sample.

ALS Chemex

EXCELLENCE IN ANALYTICAL CHEMISTRY

ALS Canada Ltd.

212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: STRATEGIC METALS LTD.
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO

Finalized Date: 25-JUN-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07060639

Sample Description	Method	WEI-21	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41
	Analyte	Recvd Wt.	Ag	Al	As	Au	B	Ba	Be	Bi	Ca	Cd	Ce	Co	Cr	Cs
	Units	kg	ppm	%	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppm	ppm	ppm
	LOR	0.02	0.01	0.01	0.1	0.2	10	10	0.05	0.01	0.01	0.01	0.02	0.1	1	0.05
CC20250		0.10	0.78	0.66	20.1	<0.2	10	960	0.49	0.13	3.09	12.50	19.80	11.5	15	1.08
CC20251		0.18	0.35	1.36	9.7	<0.2	<10	1260	0.32	0.14	0.24	0.58	23.40	7.3	23	0.74
CC20252		0.08	0.39	0.98	6.4	<0.2	<10	310	0.18	0.11	0.25	0.62	15.80	2.5	19	0.73
CC20253		0.10	1.27	0.15	18.6	<0.2	<10	360	0.07	<0.01	0.99	0.86	4.39	2.0	4	0.10
CC20254		0.08	0.36	0.11	3.1	<0.2	<10	260	<0.05	<0.01	0.94	3.19	2.14	1.4	2	0.10
CC20255		0.10	0.24	0.15	3.0	<0.2	<10	370	0.08	<0.01	0.79	2.31	4.60	1.7	1	0.11
CC20256		0.28	0.33	1.54	8.8	<0.2	<10	520	0.40	0.16	0.20	1.20	27.70	4.8	25	0.81
CC20257		0.26	0.24	1.56	11.4	<0.2	<10	510	0.42	0.16	0.28	0.80	22.50	7.0	24	0.89
CC20258		0.10	0.32	0.45	3.7	<0.2	<10	470	0.30	0.06	1.74	5.03	8.80	3.5	8	0.42
CC20259		0.14	0.20	0.77	4.0	<0.2	<10	390	0.17	0.09	1.24	5.37	9.48	3.2	13	0.52
CC20260		0.12	0.79	0.27	7.5	<0.2	<10	760	0.16	0.06	0.95	3.26	8.14	4.2	6	0.09
CC20261		0.12	0.30	0.35	3.1	<0.2	10	1550	0.51	0.04	3.92	4.35	15.70	20.8	5	0.14
CC20262		0.08	0.08	0.12	0.8	<0.2	10	540	0.14	0.03	2.36	3.42	2.28	1.2	2	0.19
CC20263		0.16	0.64	1.03	5.9	<0.2	<10	2390	0.47	0.15	1.50	0.58	18.70	10.1	16	0.52
CC20264		0.14	0.63	0.88	3.4	<0.2	<10	2260	0.61	0.11	2.40	2.64	17.10	9.9	12	0.43
CC20265		0.20	0.59	0.99	2.5	<0.2	<10	1990	0.29	0.14	0.91	0.23	14.75	2.5	15	0.53
CC20266		0.20	0.72	0.97	7.1	<0.2	<10	1860	0.28	0.18	0.89	0.20	15.65	7.2	16	0.69
CC20267		0.08	0.13	0.22	1.4	<0.2	<10	1070	0.14	0.04	1.28	0.51	4.55	1.6	4	0.19
CC20268		0.10	0.87	0.60	9.2	<0.2	10	4270	0.33	0.21	1.62	1.73	15.15	10.5	13	0.34
CC20269		0.06	0.17	0.14	2.4	<0.2	10	680	0.09	0.05	2.43	0.78	2.17	2.0	3	0.22
CC20270		0.18	2.00	0.62	14.9	<0.2	10	3800	0.46	0.25	3.94	1.83	20.60	15.6	13	0.39
CC20271		0.20	0.62	0.96	7.9	<0.2	10	1270	0.56	0.18	5.02	1.35	32.60	9.0	18	1.31
CC20272		0.14	0.10	2.73	21.9	<0.2	<10	260	0.61	0.23	0.06	0.68	21.20	10.0	36	1.23
CC20273		0.06	1.08	1.91	41.3	<0.2	10	1620	0.57	0.27	0.79	4.33	17.90	9.8	24	1.10
CC20274		0.10	0.64	0.59	6.2	<0.2	10	1620	0.29	0.17	3.25	1.50	11.35	5.9	11	0.33
CC20275		0.10	0.39	0.88	6.8	<0.2	10	1530	0.45	0.12	2.27	1.64	16.35	7.2	14	0.41
CC20276		0.08	0.17	0.28	2.3	<0.2	<10	540	0.12	0.05	0.95	2.40	3.99	2.4	6	0.34
CC20277		0.10	0.21	0.20	4.6	<0.2	<10	720	0.15	0.03	3.97	23.90	2.41	1.2	3	0.15
CC20279		0.08	0.29	0.29	4.9	<0.2	10	1240	0.22	0.04	5.04	8.89	4.70	2.5	7	0.23
CC20280		0.12	0.44	0.40	11.1	<0.2	10	870	0.28	0.06	3.58	9.69	7.04	7.2	10	0.32
CC20281		0.10	0.46	0.51	9.9	<0.2	10	1530	0.43	0.06	3.10	10.40	8.34	5.0	12	0.40
CC20282		0.28	0.35	0.86	10.3	<0.2	<10	3110	0.45	0.18	0.52	0.68	18.70	9.7	15	0.49
CC20283		0.12	0.28	0.51	2.1	<0.2	10	1870	0.32	0.07	2.60	2.82	7.85	7.5	7	0.31
CC20284		0.16	0.48	1.16	1.5	<0.2	<10	1260	0.29	0.09	0.44	0.20	16.85	1.8	20	0.76
CC20285		0.28	0.36	1.08	5.3	<0.2	<10	1040	0.39	0.19	0.16	0.29	27.30	5.2	17	0.52
CC20286		0.28	0.37	1.13	5.2	<0.2	<10	750	0.32	0.20	0.17	0.19	21.40	5.2	18	0.50
CC20287		0.10	0.51	0.47	2.2	<0.2	<10	1890	0.20	0.08	0.52	0.81	18.15	5.8	5	0.25
CC20288		0.14	0.59	0.98	2.0	<0.2	<10	900	0.18	0.10	0.29	0.22	16.20	2.7	15	0.68
CC20289		0.22	0.64	0.77	2.7	<0.2	<10	940	0.20	0.15	0.22	0.14	18.50	2.1	13	0.54
CC20290		0.12	0.68	0.86	4.3	<0.2	<10	1290	0.31	0.13	0.73	0.95	13.15	3.3	14	0.52

omments: Interference: Ca>10% on ICP-MS As,ICP-AES results shown. Gold determinations by ME-MS41 are semi-quantitative due to the small sample weight used (0.5g). NSS is non-sufficient sample.

ALS Chemex

EXCELLENCE IN ANALYTICAL CHEMISTRY

ALS Canada Ltd.

212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: STRATEGIC METALS LTD.
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO

Finalized Date: 25-JUN-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07060639

Sample Description	Method	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41
	Analyte	Cu	Fe	Ga	Ge	Hf	Hg	In	K	La	Li	Mg	Mn	Mo	Na	Nb
	Units	ppm	%	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	%	ppm	ppm	%	ppm
	LOR	0.2	0.01	0.05	0.05	0.02	0.01	0.005	0.01	0.2	0.1	0.01	5	0.05	0.01	0.05
CC20250		85.7	4.03	1.43	0.15	0.16	0.29	0.034	0.15	10.3	3.0	1.05	225	25.80	0.02	0.11
CC20251		16.9	2.05	3.93	0.08	0.05	0.09	0.028	0.06	12.1	9.7	0.29	204	11.60	0.01	0.60
CC20252		11.7	1.26	3.43	0.06	0.03	0.13	0.016	0.06	8.3	5.5	0.17	48	6.60	0.02	0.46
CC20253		14.8	0.60	0.28	0.23	0.22	0.14	0.013	0.04	2.0	0.3	0.10	51	13.85	0.04	0.25
CC20254		6.2	0.39	0.29	<0.05	0.02	0.10	<0.005	0.07	1.1	0.4	0.09	41	20.20	0.03	0.06
CC20255		7.8	0.64	0.27	<0.05	0.02	0.12	<0.005	0.04	2.1	0.2	0.08	52	20.00	0.03	0.07
CC20256		23.7	1.90	4.51	0.09	0.05	0.12	0.028	0.07	14.3	10.6	0.32	83	6.28	0.01	0.63
CC20257		14.3	2.40	4.68	0.09	0.04	0.10	0.028	0.07	11.7	10.6	0.32	196	9.62	0.01	0.63
CC20258		16.4	0.71	1.00	<0.05	0.03	0.13	0.013	0.04	4.5	1.7	0.13	45	9.75	0.02	0.13
CC20259		13.5	0.93	2.23	<0.05	0.05	0.12	0.014	0.06	4.9	4.9	0.24	89	8.31	0.02	0.32
CC20260		16.1	1.42	0.33	<0.05	0.02	0.15	0.013	0.04	3.9	0.5	0.09	49	11.90	0.02	0.09
CC20261		36.4	0.85	0.52	<0.05	0.07	0.10	0.008	0.03	7.8	0.9	0.24	3520	4.15	0.02	0.07
CC20262		13.8	0.22	0.30	<0.05	0.02	0.12	<0.005	0.05	1.4	0.7	0.13	211	5.42	0.03	<0.05
CC20263		29.5	2.20	2.37	0.05	0.08	0.13	0.023	0.07	10.0	5.4	0.23	654	3.19	0.01	0.28
CC20264		58.9	1.52	1.97	<0.05	0.07	0.10	0.017	0.05	9.2	4.3	0.20	777	2.01	0.01	0.21
CC20265		14.3	1.21	2.77	<0.05	0.04	0.13	0.014	0.06	7.7	6.1	0.22	65	0.74	0.01	0.27
CC20266		15.8	2.85	2.85	0.05	0.03	0.13	0.018	0.06	8.3	5.1	0.19	343	3.38	0.01	0.35
CC20267		8.7	0.56	0.50	<0.05	0.02	0.11	0.005	0.05	2.5	0.9	0.13	68	1.72	0.02	0.06
CC20268		71.6	3.05	1.17	0.06	0.12	0.10	0.029	0.15	8.2	2.0	0.41	199	7.00	<0.01	0.07
CC20269		14.6	0.57	0.34	<0.05	0.04	0.14	0.005	0.04	1.2	0.6	0.26	34	2.23	0.03	<0.05
CC20270		61.8	3.78	1.05	0.07	0.13	0.27	0.033	0.16	11.5	1.9	1.27	252	33.70	0.01	0.08
CC20271		49.2	2.42	2.76	0.08	0.08	0.14	0.026	0.19	17.8	12.2	1.73	258	4.38	0.02	0.13
CC20272		30.2	3.50	5.71	0.06	0.13	0.04	0.045	0.09	11.1	21.6	0.37	186	23.10	0.01	0.93
CC20273		49.4	4.11	5.01	0.13	0.07	0.31	0.045	0.18	10.0	6.3	0.16	230	54.20	0.01	0.44
CC20274		37.8	1.70	1.40	<0.05	0.08	0.10	0.020	0.06	6.4	3.1	0.27	173	3.59	0.01	0.17
CC20275		30.7	1.74	2.04	<0.05	0.08	0.12	0.021	0.07	8.9	5.7	0.23	444	3.78	0.01	0.27
CC20276		9.4	0.47	0.84	<0.05	0.02	0.12	0.006	0.07	2.3	1.2	0.07	60	8.56	0.03	0.11
CC20277		16.9	0.24	0.49	<0.05	0.04	0.11	<0.005	0.02	1.4	0.6	0.05	66	5.61	0.02	0.08
CC20279		23.9	0.41	0.72	0.05	0.07	0.13	0.005	0.03	3.2	1.3	0.23	396	3.96	0.03	0.11
CC20280		32.3	0.75	1.02	0.06	0.07	0.17	0.009	0.03	4.1	1.6	0.23	869	12.55	0.02	0.15
CC20281		40.7	0.82	1.28	<0.05	0.10	0.16	0.012	0.04	4.8	2.1	0.23	519	16.15	0.02	0.18
CC20282		28.8	2.54	2.25	0.06	0.06	0.14	0.026	0.10	9.4	4.4	0.16	417	5.83	<0.01	0.20
CC20283		29.8	0.89	1.08	<0.05	0.07	0.11	0.010	0.05	4.0	2.1	0.32	1055	2.54	0.01	0.13
CC20284		13.6	0.90	3.68	<0.05	0.03	0.10	0.014	0.07	9.1	5.4	0.24	37	0.76	<0.01	0.30
CC20285		26.0	1.96	3.17	0.06	0.03	0.07	0.022	0.07	14.0	7.4	0.22	91	1.51	<0.01	0.30
CC20286		16.3	1.95	3.37	<0.05	0.03	0.09	0.020	0.06	11.2	8.3	0.25	131	1.38	<0.01	0.28
CC20287		25.7	1.58	0.86	0.05	0.03	0.13	0.012	0.04	8.9	1.0	0.08	58	1.42	0.01	0.12
CC20288		18.2	1.12	3.22	<0.05	0.02	0.13	0.013	0.06	8.7	3.9	0.15	42	1.15	0.01	0.26
CC20289		18.2	1.25	2.54	<0.05	0.02	0.14	0.013	0.06	9.6	4.3	0.16	35	0.71	<0.01	0.21
CC20290		16.8	1.52	2.43	<0.05	0.05	0.13	0.019	0.07	7.2	4.1	0.20	78	2.27	0.01	0.23

Comments: Interference: Ca>10% on ICP-MS As,ICP-AES results shown. Gold determinations by ME-MS41 are semi-quantitative due to the small sample weight used (0.5g). NSS is non-sufficient sample.

ALS Chemex

EXCELLENCE IN ANALYTICAL CHEMISTRY

ALS Canada Ltd.

212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: STRATEGIC METALS LTD.
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO

Finalized Date: 25-JUN-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07060639

Sample Description	Method	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41
	Analyte	Ni	P	Pb	Rb	Re	S	Sb	Sc	Se	Sn	Sr	Ta	Te	Th	Ti
	Units	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%
	LOR	0.2	10	0.2	0.1	0.001	0.01	0.05	0.1	0.2	0.2	0.2	0.01	0.01	0.2	0.005
CC20250		112.0	960	10.4	8.8	0.018	0.31	7.56	4.7	7.4	0.3	175.0	0.01	0.08	3.8	<0.005
CC20251		22.7	450	10.7	10.1	0.005	0.04	3.34	2.7	2.8	0.5	26.6	<0.01	0.05	3.0	0.014
CC20252		13.6	530	8.7	8.1	0.007	0.06	3.83	2.0	3.6	0.4	21.7	<0.01	0.06	1.6	0.009
CC20253		9.3	690	13.0	1.3	0.007	0.11	9.31	0.9	2.2	2.1	46.2	0.17	0.24	0.4	<0.005
CC20254		5.4	790	3.2	2.7	0.002	0.10	4.53	0.4	1.3	0.3	39.9	0.03	0.02	0.2	<0.005
CC20255		10.6	940	3.4	2.1	0.003	0.12	2.19	0.7	1.6	0.3	38.6	0.03	0.02	0.3	<0.005
CC20256		28.6	490	11.0	11.4	0.002	0.02	2.48	3.7	2.4	0.6	21.8	<0.01	0.06	3.6	0.014
CC20257		25.3	440	11.4	12.4	0.004	0.02	2.02	2.9	2.6	0.6	22.4	<0.01	0.06	3.2	0.013
CC20258		18.7	1020	13.6	2.8	0.002	0.17	1.51	1.1	1.7	1.5	61.3	<0.01	0.03	0.5	0.006
CC20259		19.0	820	11.4	5.4	0.004	0.13	1.43	1.8	1.8	0.3	52.8	<0.01	0.04	1.2	0.008
CC20260		33.0	1240	17.0	1.7	0.017	0.18	1.73	1.9	3.5	2.9	43.2	<0.01	0.04	0.6	0.006
CC20261		51.9	930	6.8	1.3	0.003	0.24	1.38	0.9	2.8	0.5	146.5	<0.01	0.03	0.4	<0.005
CC20262		9.2	900	2.8	2.1	<0.001	0.19	0.33	0.4	1.1	0.2	67.2	<0.01	0.02	0.2	<0.005
CC20263		28.9	840	10.0	8.3	0.003	0.10	1.16	2.8	2.4	0.3	54.8	<0.01	0.05	2.0	0.006
CC20264		53.6	1190	7.8	7.0	0.003	0.15	0.87	2.0	2.2	0.3	92.8	<0.01	0.05	1.1	0.005
CC20265		13.7	740	6.9	9.2	0.003	0.08	0.46	2.1	1.5	0.3	43.4	<0.01	0.04	1.7	0.006
CC20266		13.1	970	9.4	8.9	0.004	0.10	0.59	2.6	2.1	0.4	44.6	<0.01	0.05	1.7	0.007
CC20267		7.3	890	4.4	2.8	0.001	0.16	0.47	0.8	1.0	0.2	57.4	<0.01	0.02	0.4	<0.005
CC20268		71.3	920	11.4	6.3	0.007	0.17	2.94	3.5	5.4	0.2	53.6	<0.01	0.10	2.1	<0.005
CC20269		11.5	570	3.9	2.2	0.001	0.20	0.86	0.7	4.7	<0.2	146.5	<0.01	0.03	0.4	<0.005
CC20270		122.5	750	17.6	7.3	0.012	0.18	5.24	4.6	6.5	0.2	119.5	<0.01	0.09	1.7	<0.005
CC20271		37.6	2500	12.9	11.5	0.006	0.22	2.01	3.8	3.0	0.3	99.6	<0.01	0.07	4.2	0.005
CC20272		37.5	300	12.0	14.6	<0.001	0.04	4.01	3.8	4.6	0.7	17.0	<0.01	0.09	5.4	0.022
CC20273		150.0	1130	18.1	15.8	0.035	0.14	5.72	4.9	21.7	0.9	92.0	<0.01	0.17	1.7	<0.005
CC20274		34.3	840	7.8	5.8	0.003	0.19	1.51	1.9	4.1	0.2	98.8	<0.01	0.06	0.9	0.005
CC20275		34.7	920	7.9	7.4	0.006	0.14	1.66	2.4	2.9	0.3	66.0	<0.01	0.05	1.5	0.007
CC20276		30.1	730	6.7	3.3	0.005	0.14	2.12	1.0	1.8	0.3	51.8	<0.01	0.03	0.4	<0.005
CC20277		58.7	660	2.3	0.8	0.010	0.22	6.24	0.5	8.6	<0.2	195.0	<0.01	0.03	0.2	0.005
CC20279		45.6	980	5.2	1.8	0.027	0.22	3.03	0.7	10.5	<0.2	220.0	<0.01	0.03	0.3	<0.005
CC20280		91.0	1030	6.7	1.9	0.034	0.22	5.13	1.0	9.3	0.2	170.5	<0.01	0.04	0.4	0.005
CC20281		135.5	880	5.0	4.2	0.003	0.18	7.72	1.4	3.2	0.2	165.0	<0.01	0.06	0.7	0.005
CC20282		25.5	750	9.6	9.0	0.003	0.05	1.75	3.0	1.9	0.3	37.2	<0.01	0.06	2.7	0.005
CC20283		43.5	1070	4.8	5.0	0.003	0.18	0.85	1.3	1.8	<0.2	159.0	<0.01	0.05	0.6	0.005
CC20284		12.3	610	5.0	9.4	0.002	0.05	0.29	2.2	1.1	0.4	32.8	<0.01	0.04	1.9	0.005
CC20285		20.5	640	10.6	8.7	0.002	0.02	0.65	2.7	1.8	0.3	19.2	<0.01	0.05	3.3	0.007
CC20286		16.9	630	10.4	8.8	0.001	0.02	0.56	1.9	1.4	0.3	19.1	<0.01	0.04	2.1	0.008
CC20287		28.2	1540	4.3	3.3	0.001	0.17	0.73	1.8	1.9	<0.2	38.2	<0.01	0.04	0.8	0.005
CC20288		12.1	860	5.8	8.1	0.001	0.08	0.39	1.9	1.4	0.3	23.5	<0.01	0.05	1.4	0.005
CC20289		11.7	550	7.8	7.6	0.002	0.04	0.35	1.8	1.6	0.2	19.3	<0.01	0.04	2.1	0.006
CC20290		12.0	900	8.4	6.8	0.001	0.10	0.76	2.5	1.8	0.3	48.4	<0.01	0.04	1.5	0.005

Comments: Interference: Ca>10% on ICP-MS As,ICP-AES results shown. Gold determinations by ME-MS41 are semi-quantitative due to the small sample weight used (0.5g). NSS is non-sufficient sample.

ALS Chemex

EXCELLENCE IN ANALYTICAL CHEMISTRY

ALS Canada Ltd.

212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: STRATEGIC METALS LTD.
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO

Finalized Date: 25-JUN-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07060639

Sample Description	Method	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41
	Analyte	Tl	U	V	W	Y	Zn	Zr
	Units	ppm	ppm	ppm	ppm	ppm	ppm	ppm
	LOR	0.02	0.05	1	0.05	0.05	2	0.5
CC20250		0.68	5.34	112	0.12	28.40	853	7.0
CC20251		0.56	2.21	112	0.16	6.64	104	1.3
CC20252		0.50	1.66	62	0.15	3.80	48	0.9
CC20253		0.05	0.84	10	0.16	3.26	36	0.7
CC20254		0.04	0.35	12	0.12	1.52	40	<0.5
CC20255		0.02	0.82	7	0.09	4.19	37	<0.5
CC20256		0.61	2.19	95	0.12	10.35	100	1.4
CC20257		0.53	1.45	97	0.15	5.38	106	1.1
CC20258		0.09	1.05	20	0.07	5.80	54	0.9
CC20259		0.28	1.02	45	0.07	3.30	93	1.7
CC20260		0.13	1.38	10	0.06	7.80	63	0.7
CC20261		0.04	0.98	15	<0.05	14.30	215	2.1
CC20262		0.03	0.17	5	<0.05	1.67	142	0.7
CC20263		0.12	1.64	48	0.07	11.10	109	2.3
CC20264		0.06	1.17	31	0.07	12.75	143	1.9
CC20265		0.10	0.91	27	0.06	5.06	57	1.0
CC20266		0.11	1.20	44	0.08	6.01	54	1.0
CC20267		0.02	0.33	6	<0.05	3.11	43	0.6
CC20268		0.12	1.50	59	0.05	11.80	296	4.6
CC20269		0.06	1.56	10	<0.05	1.50	86	1.5
CC20270		0.46	3.69	144	0.06	18.15	204	4.4
CC20271		0.14	2.23	78	0.06	16.75	226	3.3
CC20272		1.18	1.51	146	0.18	3.69	107	4.9
CC20273		3.08	4.92	250	0.25	16.55	262	2.8
CC20274		0.10	1.86	43	0.05	7.54	150	2.7
CC20275		0.17	1.76	57	0.06	10.35	157	2.7
CC20276		0.28	0.51	26	<0.05	2.42	130	0.7
CC20277		0.13	0.30	72	<0.05	2.24	900	1.5
CC20279		0.12	16.45	99	0.05	6.24	346	2.4
CC20280		0.19	2.95	98	0.07	8.13	342	2.8
CC20281		0.31	2.61	143	0.07	11.35	734	3.8
CC20282		0.12	1.67	67	0.15	11.60	121	1.5
CC20283		0.05	0.79	21	<0.05	5.86	130	2.0
CC20284		0.14	0.83	33	0.10	4.01	45	0.8
CC20285		0.10	1.12	38	0.08	9.17	77	0.8
CC20286		0.09	0.82	39	0.10	5.18	79	0.5
CC20287		0.03	1.27	7	0.05	15.60	61	0.7
CC20288		0.11	0.94	26	0.07	5.76	44	0.6
CC20289		0.08	0.64	19	<0.05	4.70	42	0.7
CC20290		0.10	1.19	45	0.05	6.44	57	1.7

Comments: Interference: Ca>10% on ICP-MS As,ICP-AES results shown. Gold determinations by ME-MS41 are semi-quantitative due to the small sample weight used (0.5g). NSS is non-sufficient sample.

ALS Chemex

EXCELLENCE IN ANALYTICAL CHEMISTRY

ALS Canada Ltd.

212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: STRATEGIC METALS LTD.
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO

Finalized Date: 25-JUN-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07060639

Sample Description	Method	WEI-21	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41
	Analyte	Recvd Wt.	Ag	Al	As	Au	B	Ba	Be	Bi	Ca	Cd	Ce	Co	Cr	Cs
	Units	kg	ppm	%	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppm	ppm	ppm
	LOR	0.02	0.01	0.01	0.1	0.2	10	10	0.05	0.01	0.01	0.01	0.02	0.1	1	0.05
CC20291		0.14	1.53	1.48	7.0	<0.2	<10	2030	0.51	0.25	0.55	0.37	24.00	11.8	23	1.04
CC20292		0.20	0.73	1.10	6.7	<0.2	<10	1420	0.40	0.20	0.26	0.39	19.70	4.2	18	0.69
CC20293		0.18	0.42	1.05	5.8	<0.2	<10	1050	0.29	0.18	0.23	0.65	16.95	4.7	17	0.65
CC20294		0.18	0.56	1.05	8.7	<0.2	<10	2760	0.38	0.20	0.39	0.59	20.80	9.5	17	0.65
CC202300		0.14	0.05	0.80	15.6	<0.2	<10	240	0.20	0.17	0.04	0.41	21.50	3.4	14	0.66
CC202301		0.08	0.27	0.74	14.0	<0.2	<10	470	0.21	0.27	0.06	0.44	24.60	2.6	18	1.15
CC202302		0.14	0.29	1.76	24.4	<0.2	<10	790	0.71	0.36	0.38	0.27	49.30	5.8	31	1.58
CC202303		0.08	0.37	2.10	24.4	<0.2	<10	790	0.66	0.38	0.25	0.37	39.50	6.5	36	1.93
CC202304		0.12	0.24	1.53	10.9	<0.2	<10	200	0.27	0.20	0.03	0.07	25.50	2.7	20	1.21
CC202305		0.12	0.36	1.57	22.1	<0.2	<10	880	0.67	0.32	0.22	0.13	38.20	7.3	25	1.42
CC202306		0.10	0.17	1.82	13.8	<0.2	<10	340	0.58	0.26	0.10	0.17	35.00	6.4	27	1.28
CC202307		0.10	0.17	1.69	16.7	<0.2	<10	450	0.58	0.34	0.06	0.13	25.60	6.4	31	1.52
CC202308		0.08	0.29	1.09	17.0	<0.2	<10	230	0.53	0.22	0.11	0.36	23.40	7.3	18	1.46
CC202309		0.12	0.26	0.98	19.7	<0.2	<10	410	0.75	0.28	0.10	0.70	35.20	9.2	18	1.47
CC202310		0.12	0.43	0.88	18.8	<0.2	<10	510	0.66	0.27	0.33	0.40	31.70	10.5	22	0.98
CC202311		0.06	0.21	0.92	11.9	<0.2	<10	530	0.28	0.23	0.22	0.61	27.40	5.3	14	0.94
CC202312		0.04	0.17	0.43	4.7	<0.2	10	700	0.23	0.04	4.21	0.64	7.75	3.2	6	0.35
CC202313		0.04	0.21	0.35	5.4	<0.2	<10	940	0.19	0.03	3.38	0.94	7.63	3.2	5	0.55
CC202326		0.06	0.37	0.57	15.3	<0.2	<10	470	0.23	0.13	0.13	1.06	10.40	1.3	20	0.89
CC202327		0.18	0.32	0.49	24.2	<0.2	<10	650	0.31	0.11	0.12	2.70	17.55	5.8	14	0.41
CC202328		0.20	0.10	2.47	24.9	<0.2	<10	400	0.61	0.18	0.06	0.58	24.40	10.7	36	1.12
CC202329		0.18	0.27	2.72	16.2	<0.2	<10	190	0.51	0.18	0.05	0.37	23.50	10.0	34	1.17
CC202330		0.22	0.32	2.19	28.0	<0.2	<10	160	0.40	0.20	0.03	0.19	20.60	6.6	35	1.26
CC202331		0.20	1.26	0.68	17.8	<0.2	<10	330	0.18	0.17	0.04	0.47	12.05	1.3	20	0.58
CC202332		0.18	1.11	0.60	5.3	<0.2	<10	220	0.14	0.11	0.02	0.39	11.10	0.5	11	0.68
CC202337		0.08	0.62	0.54	29.6	<0.2	<10	760	0.23	0.18	0.08	0.64	14.75	1.6	23	0.89
CC202338		0.04	1.84	0.28	5.2	<0.2	<10	420	0.11	0.02	0.21	1.59	3.70	0.8	8	0.50
CC202339		0.06	1.70	0.91	45.8	<0.2	<10	450	0.27	0.24	0.03	0.18	14.75	2.1	32	1.00
CC202340		0.06	1.03	0.70	36.5	<0.2	<10	220	0.13	0.23	0.04	0.07	14.20	2.4	20	0.71
CC202341		0.06	0.59	1.93	28.3	<0.2	<10	200	0.51	0.21	0.05	0.25	20.80	6.9	33	1.17
CC202342		0.08	0.75	1.16	87.3	<0.2	<10	440	0.36	0.21	0.03	0.23	21.80	3.9	41	0.89
CC202343		0.30	0.09	1.06	24.8	<0.2	<10	140	0.19	0.17	0.02	0.09	22.80	2.7	19	1.20
CC202344		0.16	0.28	2.13	17.7	<0.2	<10	160	0.39	0.17	0.04	0.15	20.50	5.6	29	1.25
CC202345		0.02	0.87	0.28	6.7	<0.2	<10	790	0.11	<0.01	0.70	3.87	3.53	2.0	4	0.41
CC202346		0.02	1.01	0.57	10.2	<0.2	<10	300	0.16	0.05	0.39	1.31	9.65	1.3	11	0.72
CC202347		0.02	0.71	0.43	11.5	<0.2	<10	280	0.10	<0.01	0.45	0.95	5.26	1.5	2	0.09
CC202348		0.08	0.68	0.55	15.8	<0.2	<10	580	0.22	0.13	0.06	1.29	11.50	1.4	16	1.01
CC202349		Not Recvd														
CC202350		Not Recvd														
CC202351		0.20	0.51	1.64	11.9	<0.2	<10	430	0.72	0.12	1.30	1.56	33.80	8.8	30	0.90

Comments: Interference: Ca>10% on ICP-MS As,ICP-AES results shown. Gold determinations by ME-MS41 are semi-quantitative due to the small sample weight used (0.5g). NSS is non-sufficient sample.

ALS Chemex

EXCELLENCE IN ANALYTICAL CHEMISTRY

ALS Canada Ltd.

212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: STRATEGIC METALS LTD.
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO

Finalized Date: 25-JUN-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07060639

Sample Description	Method	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41
	Analyte	Cu	Fe	Ga	Ge	Hf	Hg	In	K	La	Li	Mg	Mn	Mo	Na	Nb
	Units	ppm	%	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	%	ppm	ppm	%	ppm
	LOR	0.2	0.01	0.05	0.05	0.02	0.01	0.005	0.01	0.2	0.1	0.01	5	0.05	0.01	0.05
CC20291		32.5	2.62	4.16	0.07	0.07	0.17	0.032	0.07	12.3	7.2	0.26	255	4.75	<0.01	0.37
CC20292		23.5	1.90	3.33	<0.05	0.03	0.12	0.024	0.07	10.2	7.6	0.20	55	1.96	<0.01	0.32
CC20293		15.1	1.73	3.50	<0.05	0.03	0.10	0.019	0.06	9.1	7.0	0.20	85	2.35	<0.01	0.34
CC20294		25.9	2.49	2.92	0.05	0.04	0.12	0.025	0.10	10.1	5.2	0.18	253	4.37	<0.01	0.28
CC202300		15.1	2.06	5.22	0.07	<0.02	0.03	0.022	0.05	11.4	2.2	0.07	66	16.75	0.01	0.57
CC202301		22.1	2.26	5.40	0.08	0.02	0.08	0.031	0.12	15.4	1.8	0.06	48	6.75	0.01	0.56
CC202302		28.5	3.80	6.57	0.15	0.05	0.09	0.062	0.19	28.9	8.9	0.18	163	6.22	0.01	0.76
CC202303		28.7	4.80	7.04	0.13	0.05	0.09	0.067	0.20	25.7	8.6	0.22	160	6.53	0.02	0.79
CC202304		12.1	2.15	7.32	0.08	<0.02	0.04	0.027	0.05	14.4	6.8	0.07	55	2.54	0.01	0.70
CC202305		35.6	3.83	5.53	0.13	0.05	0.09	0.052	0.17	25.3	9.7	0.15	100	3.15	0.01	0.38
CC202306		25.8	3.28	6.72	0.11	0.04	0.04	0.043	0.08	21.3	8.3	0.23	134	2.63	0.01	0.55
CC202307		32.1	4.17	8.18	0.10	0.03	0.04	0.057	0.08	15.6	5.2	0.14	94	5.99	0.01	0.19
CC202308		31.7	3.10	4.45	0.10	0.03	0.06	0.041	0.07	13.2	5.3	0.09	80	9.54	0.01	0.31
CC202309		47.5	3.97	4.91	0.14	0.04	0.09	0.048	0.11	20.5	3.0	0.08	98	15.05	0.01	0.60
CC202310		73.1	3.70	3.76	0.14	0.05	0.09	0.056	0.11	22.2	3.1	0.07	99	9.57	0.01	0.29
CC202311		17.8	2.07	5.89	0.08	0.02	0.04	0.029	0.08	14.3	4.2	0.07	71	5.94	0.01	0.64
CC202312		17.9	0.88	1.18	<0.05	0.07	0.10	0.014	0.05	4.0	1.3	0.11	275	2.43	0.03	0.21
CC202313		18.5	0.83	1.04	<0.05	0.08	0.12	0.013	0.05	3.8	1.3	0.09	222	2.90	0.02	0.16
CC202326		24.8	1.22	4.85	0.05	<0.02	0.04	0.019	0.10	6.0	0.8	0.05	22	35.40	0.02	0.29
CC202327		35.8	2.51	1.87	0.11	0.11	0.09	0.035	0.10	9.4	4.0	0.12	81	39.10	0.01	0.30
CC202328		43.3	3.64	6.09	0.12	0.16	0.03	0.042	0.10	12.5	16.9	0.34	294	20.20	0.01	1.07
CC202329		25.2	3.23	6.33	0.09	0.19	0.05	0.038	0.06	11.9	21.6	0.35	214	10.10	0.01	1.32
CC202330		19.4	3.83	7.62	0.11	0.09	0.04	0.047	0.06	10.8	19.4	0.27	154	25.20	0.01	1.24
CC202331		15.3	1.45	5.08	0.07	<0.02	0.03	0.022	0.07	7.2	1.1	0.04	29	33.60	0.01	0.25
CC202332		13.3	0.70	3.61	<0.05	<0.02	0.07	0.016	0.04	6.3	0.7	0.02	9	8.33	0.01	0.21
CC202337		42.3	1.53	3.57	0.17	0.02	0.18	0.033	0.16	8.1	0.8	0.03	18	54.10	0.02	0.15
CC202338		14.4	0.42	1.27	0.06	0.02	0.14	0.010	0.07	2.1	0.3	0.03	39	14.35	0.03	0.11
CC202339		33.6	3.16	7.20	0.21	0.02	0.16	0.038	0.26	8.9	3.7	0.09	120	98.80	0.01	0.39
CC202340		17.2	3.68	8.48	0.11	0.02	0.10	0.022	0.15	7.6	2.4	0.08	80	86.30	0.01	1.03
CC202341		28.2	3.66	6.75	0.11	0.09	0.06	0.045	0.08	10.8	20.5	0.26	138	18.10	0.01	1.18
CC202342		28.3	4.11	6.97	0.15	0.04	0.05	0.069	0.14	11.5	7.4	0.18	131	53.20	0.01	0.82
CC202343		10.9	2.49	6.52	0.08	0.06	0.02	0.023	0.05	12.0	4.3	0.10	79	20.50	0.01	0.86
CC202344		14.0	3.10	6.38	0.07	0.10	0.03	0.038	0.05	10.7	25.2	0.22	142	10.50	<0.01	1.33
CC202345		14.1	0.46	0.77	0.09	0.03	0.19	0.010	0.08	1.7	0.5	0.05	49	22.80	0.04	0.11
CC202346		28.8	1.11	1.76	0.15	0.04	0.31	0.023	0.06	4.9	0.7	0.04	37	23.10	0.03	0.16
CC202347		14.9	1.68	0.45	0.07	0.02	0.11	0.011	0.06	2.6	0.2	0.04	63	21.60	0.06	0.07
CC202348		26.5	1.39	4.32	0.05	<0.02	0.08	0.030	0.09	6.1	0.6	0.03	38	30.70	0.02	0.29
CC202349																
CC202350																
CC202351		36.8	2.29	5.08	0.10	0.13	0.08	0.028	0.08	19.2	18.4	0.68	299	1.64	0.02	0.80

Comments: Interference: Ca>10% on ICP-MS As,ICP-AES results shown. Gold determinations by ME-MS41 are semi-quantitative due to the small sample weight used (0.5g). NSS is non-sufficient sample.

ALS Chemex

EXCELLENCE IN ANALYTICAL CHEMISTRY

ALS Canada Ltd.

212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: STRATEGIC METALS LTD.
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO

Finalized Date: 25-JUN-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07060639

Sample Description	Method	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41
	Analyte	Ni	P	Pb	Rb	Re	S	Sb	Sc	Se	Sn	Sr	Ta	Te	Th	Ti
	Units	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%
	LOR	0.2	10	0.2	0.1	0.001	0.01	0.05	0.1	0.2	0.2	0.2	0.01	0.01	0.2	0.005
CC20291		29.5	1020	14.3	9.3	0.006	0.09	1.04	3.9	2.8	0.4	43.7	<0.01	0.06	1.9	0.006
CC20292		18.7	470	12.0	10.8	0.002	0.03	1.03	3.1	2.1	0.3	24.9	<0.01	0.06	3.0	0.007
CC20293		14.4	610	9.8	10.5	0.001	0.04	0.65	2.4	1.5	0.3	23.5	<0.01	0.05	2.2	0.007
CC20294		22.2	780	12.1	10.5	0.001	0.04	1.18	3.3	1.6	0.3	32.7	<0.01	0.05	2.6	0.006
CC202300		32.2	220	11.0	7.7	<0.001	0.03	2.24	1.6	1.7	0.7	8.5	<0.01	0.07	0.8	0.022
CC202301		14.8	2350	25.2	7.3	0.001	0.23	1.42	1.1	2.0	0.7	21.0	0.01	0.12	0.3	0.015
CC202302		23.6	6110	35.0	11.8	0.001	0.31	1.32	3.4	3.1	0.7	39.1	0.01	0.21	2.9	0.024
CC202303		28.8	7370	35.5	13.9	<0.001	0.30	1.45	2.9	3.1	0.8	42.6	0.01	0.22	1.2	0.021
CC202304		8.9	1400	16.6	6.2	<0.001	0.04	0.47	1.6	1.1	0.9	10.5	<0.01	0.07	1.0	0.018
CC202305		37.3	5500	42.8	12.3	0.001	0.32	1.50	2.3	3.8	0.6	49.6	<0.01	0.19	0.9	0.011
CC202306		26.5	3950	17.4	10.9	0.001	0.05	0.96	2.2	1.7	0.7	14.9	0.01	0.08	0.8	0.019
CC202307		34.8	4780	22.9	8.5	<0.001	0.05	1.51	1.1	2.3	0.8	13.0	<0.01	0.12	0.2	0.008
CC202308		45.8	1830	20.6	9.5	0.001	0.03	2.26	1.7	2.7	0.6	9.3	<0.01	0.15	0.6	0.013
CC202309		48.9	3270	33.5	14.7	0.002	0.06	2.92	3.8	4.3	0.5	14.3	<0.01	0.14	2.4	0.018
CC202310		78.4	2690	29.9	10.5	0.002	0.11	3.14	3.3	8.7	0.5	30.2	<0.01	0.21	2.3	0.008
CC202311		24.3	680	12.5	10.3	0.001	0.03	1.02	2.1	1.6	0.7	13.9	<0.01	0.10	1.2	0.018
CC202312		17.1	930	4.2	3.7	0.002	0.25	0.81	1.2	2.1	0.2	103.5	0.03	0.05	0.4	0.008
CC202313		22.8	850	4.2	4.7	0.002	0.23	0.64	1.2	1.8	0.2	86.7	0.03	0.05	0.5	0.005
CC202326		28.7	550	12.3	13.9	0.003	0.09	5.48	1.4	3.7	0.9	26.8	<0.01	0.14	0.3	0.009
CC202327		79.6	420	9.9	6.4	0.005	0.20	5.07	3.5	6.1	0.5	46.0	<0.01	0.08	4.4	0.013
CC202328		41.1	360	11.5	14.0	<0.001	0.09	2.74	4.3	11.1	0.7	29.6	<0.01	0.13	5.0	0.028
CC202329		28.2	250	12.6	11.3	<0.001	0.03	1.69	4.4	3.2	0.9	9.7	0.01	0.07	5.1	0.033
CC202330		22.3	250	11.7	12.0	<0.001	0.03	4.28	3.7	9.6	0.8	11.7	<0.01	0.14	4.0	0.028
CC202331		8.1	570	12.5	7.5	0.001	0.11	6.61	0.6	8.4	0.8	17.7	<0.01	0.14	<0.2	0.008
CC202332		3.5	310	10.0	5.6	0.001	0.03	3.01	0.8	3.0	0.7	9.1	<0.01	0.05	0.2	0.007
CC202337		32.1	930	15.0	13.2	0.033	0.32	7.86	2.4	28.9	0.7	92.3	<0.01	0.22	0.8	<0.005
CC202338		7.4	950	5.0	3.4	0.013	0.17	2.56	1.7	11.5	0.3	18.9	0.02	0.07	0.4	0.006
CC202339		11.2	840	18.2	19.5	0.005	0.59	20.60	3.2	44.4	1.1	26.6	<0.01	0.32	0.6	0.015
CC202340		9.3	360	11.8	14.6	0.001	0.25	11.55	2.3	12.8	0.9	12.5	<0.01	0.21	2.2	0.036
CC202341		22.6	320	11.3	13.0	0.001	0.07	4.34	4.3	7.6	0.7	15.8	<0.01	0.11	4.3	0.021
CC202342		21.6	720	15.4	13.3	0.001	0.21	13.15	3.9	15.5	0.9	47.4	<0.01	0.22	3.3	0.022
CC202343		9.6	200	9.6	8.4	<0.001	0.03	3.31	2.3	4.1	0.8	11.2	<0.01	0.10	3.2	0.024
CC202344		16.8	290	11.1	12.9	<0.001	0.03	2.05	3.2	2.9	0.7	10.3	<0.01	0.08	3.8	0.021
CC202345		31.6	1220	3.0	3.2	0.040	0.20	6.73	2.5	18.5	<0.2	42.3	0.03	0.04	0.3	<0.005
CC202346		29.1	1220	6.0	6.1	0.120	0.17	9.93	4.8	25.2	0.3	41.2	0.02	0.09	0.6	0.005
CC202347		22.6	1040	2.6	1.4	0.041	0.17	6.07	2.0	9.9	<0.2	21.5	0.02	0.06	0.5	<0.005
CC202348		18.9	760	10.7	8.6	0.003	0.13	3.52	0.5	4.5	0.7	15.6	<0.01	0.12	<0.2	<0.005
CC202349																
CC202350																
CC202351		30.8	1320	20.1	9.9	0.001	0.05	1.75	4.8	1.8	0.6	41.2	<0.01	0.05	4.5	0.023

Comments: Interference: Ca>10% on ICP-MS As,ICP-AES results shown. Gold determinations by ME-MS41 are semi-quantitative due to the small sample weight used (0.5g). NSS is non-sufficient sample.

ALS Chemex

EXCELLENCE IN ANALYTICAL CHEMISTRY

ALS Canada Ltd.

212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: STRATEGIC METALS LTD.
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO

Finalized Date: 25-JUN-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07060639

Sample Description	Method	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41
	Analyte	Tl	U	V	W	Y	Zn	Zr
	Units	ppm	ppm	ppm	ppm	ppm	ppm	ppm
	LOR	0.02	0.05	1	0.05	0.05	2	0.5
CC20291		0.18	1.91	74	0.09	11.75	86	1.7
CC20292		0.14	1.26	59	0.08	6.46	74	0.9
CC20293		0.11	1.11	51	0.08	4.62	67	0.7
CC20294		0.13	1.50	67	0.08	9.65	90	1.1
CC202300		0.41	0.68	145	0.18	2.66	103	<0.5
CC202301		0.52	1.60	60	0.20	6.96	52	<0.5
CC202302		0.52	3.16	94	0.22	18.90	84	0.6
CC202303		0.52	2.51	119	0.25	12.05	114	0.6
CC202304		0.19	0.77	81	0.15	2.45	33	<0.5
CC202305		0.32	2.24	85	0.14	9.60	118	0.7
CC202306		0.17	2.17	80	0.17	12.25	96	0.5
CC202307		0.26	2.74	130	0.15	8.62	144	<0.5
CC202308		0.16	1.80	108	0.14	8.03	137	0.5
CC202309		0.16	2.55	76	0.15	14.35	178	0.7
CC202310		0.10	3.31	103	0.09	19.30	335	0.7
CC202311		0.14	1.41	111	0.14	7.33	80	<0.5
CC202312		0.05	0.56	17	0.09	4.02	56	2.1
CC202313		0.07	0.37	15	0.09	4.03	49	2.4
CC202326		1.44	2.40	270	0.26	2.70	92	<0.5
CC202327		2.00	2.68	104	0.14	12.35	228	4.5
CC202328		1.15	4.02	187	0.20	5.88	90	5.6
CC202329		0.36	1.10	110	0.17	3.48	61	5.8
CC202330		0.77	0.91	194	0.18	2.85	65	3.5
CC202331		0.89	1.58	195	0.18	3.06	20	<0.5
CC202332		0.62	1.41	88	0.11	2.79	8	<0.5
CC202337		3.03	4.39	196	0.19	6.07	67	<0.5
CC202338		0.39	1.55	57	0.12	1.49	29	0.7
CC202339		3.59	3.64	376	0.32	5.64	35	0.5
CC202340		1.85	0.96	352	0.29	2.15	37	0.9
CC202341		0.70	1.14	165	0.20	4.38	67	3.3
CC202342		2.36	2.39	419	0.23	3.80	79	1.4
CC202343		0.72	0.76	190	0.14	2.23	37	2.3
CC202344		0.47	0.64	121	0.17	2.20	59	3.1
CC202345		0.46	2.40	54	0.11	3.91	60	0.9
CC202346		1.63	5.04	69	0.15	8.34	44	1.1
CC202347		0.30	1.85	43	0.10	6.21	45	0.6
CC202348		0.84	2.21	166	0.20	2.93	56	<0.5
CC202349								
CC202350								
CC202351		0.14	1.31	102	0.23	14.90	159	4.2

Comments: Interference: Ca>10% on ICP-MS As,ICP-AES results shown. Gold determinations by ME-MS41 are semi-quantitative due to the small sample weight used (0.5g). NSS is non-sufficient sample.

ALS Chemex

EXCELLENCE IN ANALYTICAL CHEMISTRY

ALS Canada Ltd.

212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: STRATEGIC METALS LTD.
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO

Finalized Date: 25-JUN-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07060639

Sample Description	Method	WEI-21	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41
	Analyte	Recvd Wt.	Ag	Al	As	Au	B	Ba	Be	Bi	Ca	Cd	Ce	Co	Cr	Cs
	Units	kg	ppm	%	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppm	ppm	ppm
	LOR	0.02	0.01	0.01	0.1	0.2	10	10	0.05	0.01	0.01	0.01	0.02	0.1	1	0.05
CC202352		0.04	0.09	0.21	1.5	<0.2	<10	450	0.11	<0.01	2.63	0.91	1.87	4.5	2	0.20
CC202353		0.10	0.32	1.14	11.7	<0.2	<10	720	0.39	0.07	1.74	1.55	18.65	18.9	18	0.75
CC202354		0.14	0.16	0.62	4.0	<0.2	<10	1690	0.39	0.03	2.10	2.51	5.31	72.6	4	0.17
CC202355		0.12	0.13	0.48	6.6	<0.2	<10	1160	0.24	<0.01	1.76	2.45	6.86	64.7	4	0.13
CC202356		0.06	0.03	0.06	0.5	<0.2	<10	500	0.05	<0.01	0.92	0.36	1.30	2.2	1	0.06
CC202357		0.06	0.09	0.10	1.0	<0.2	<10	720	0.06	<0.01	0.83	0.21	2.24	1.8	1	0.06
CC202358		0.02	0.07	0.06	0.6	<0.2	<10	550	0.05	<0.01	0.83	0.35	1.57	2.1	1	0.08
CC202359		0.02	0.21	0.09	0.9	<0.2	<10	530	0.05	<0.01	0.76	0.21	1.81	1.5	1	0.11
CC202360		0.04	0.14	0.23	1.9	<0.2	<10	510	0.08	0.01	0.47	0.16	4.52	1.3	4	0.27
CC202361		0.06	0.44	1.50	13.0	<0.2	<10	1210	0.98	0.09	1.37	1.93	38.00	20.6	25	0.85
CC202362		0.04	0.34	1.02	5.4	<0.2	<10	690	0.40	0.10	0.25	0.70	22.80	4.2	17	0.65
CC202363		0.08	0.24	1.52	9.3	<0.2	<10	810	0.77	0.15	1.41	0.93	33.40	6.9	26	0.94
CC202364		0.08	0.32	1.63	8.2	<0.2	<10	500	0.43	0.15	0.15	0.48	27.00	4.1	27	0.85
CC202365		0.06	0.12	0.15	4.3	<0.2	<10	420	0.14	<0.01	5.08	4.49	2.45	2.4	2	0.30
CC202366		0.12	0.46	0.97	17.8	<0.2	<10	1090	0.67	0.10	1.28	9.32	27.60	10.7	18	0.75
CC202367		0.14	1.03	1.30	51.4	<0.2	<10	160	1.01	0.19	3.31	6.77	28.40	10.1	35	1.06
CC202368		0.26	0.36	0.65	19.1	<0.2	<10	320	0.53	0.11	0.41	1.91	15.15	2.3	16	0.60
CC202369		0.12	1.60	0.75	33.7	<0.2	<10	720	0.77	0.15	1.34	16.25	25.40	5.2	46	0.88
CC202370		0.06	1.39	0.76	25.3	<0.2	10	490	0.57	0.09	2.71	13.75	12.75	6.4	18	1.02
CC202371		0.12	0.40	0.68	30.4	<0.2	<10	350	0.43	0.17	0.13	0.86	14.65	5.4	16	0.89
CC202372		0.12	0.30	0.57	29.8	<0.2	<10	340	0.34	0.14	0.03	0.60	13.10	7.0	13	0.78
CC202373		0.12	0.26	0.58	36.5	<0.2	<10	330	0.40	0.14	0.04	1.40	16.30	8.4	15	0.94
CC202374		0.16	0.41	1.58	6.6	<0.2	<10	420	0.71	0.11	1.32	1.24	32.80	7.3	28	1.04
CC202375		0.08	0.36	0.73	39.5	<0.2	<10	460	0.43	0.14	0.07	1.84	19.55	13.2	17	1.09
CC202395		0.04	0.35	1.43	11.3	<0.2	<10	520	0.75	0.09	1.82	2.05	28.60	8.2	24	0.69
CC202396		0.08	0.37	1.34	9.9	<0.2	<10	370	0.64	0.08	2.53	1.74	27.20	6.8	24	0.85
CC202397		0.12	0.49	1.12	27.3	<0.2	10	2550	0.82	0.12	1.90	4.64	17.40	13.1	23	0.52
CC202398		0.06	NSS	NSS	NSS	NSS	NSS	NSS	NSS	NSS	NSS	NSS	NSS	NSS	NSS	NSS
CC202399		0.08	0.35	1.09	7.1	<0.2	<10	400	0.54	0.06	2.22	1.86	22.60	5.6	20	0.56
CC202400		0.06	0.38	1.16	7.5	<0.2	<10	460	0.63	0.07	2.73	2.59	23.10	6.0	19	0.68
CC202401		0.20	1.03	1.20	38.4	<0.2	<10	240	0.24	0.17	0.02	0.08	8.91	1.6	26	1.07
CC202402		0.14	0.82	0.78	90.5	<0.2	<10	360	0.23	0.19	0.02	0.34	10.20	1.0	30	0.84
CC202403		0.08	0.70	1.71	26.7	<0.2	<10	190	0.31	0.23	0.04	0.34	17.80	3.7	33	1.48
CC202404		0.06	1.25	2.81	32.4	<0.2	<10	990	2.19	0.16	0.44	11.25	29.50	11.8	54	1.38
CC202405		0.08	0.32	1.70	45.0	<0.2	<10	380	0.67	0.19	0.06	1.61	19.95	9.2	29	0.73
CC202406		0.08	0.13	0.96	15.9	<0.2	<10	180	0.20	0.16	0.05	0.51	20.20	3.0	16	1.02
CC202407		0.02	0.47	0.53	12.1	<0.2	<10	1830	0.61	0.10	0.53	14.75	21.00	8.8	18	0.47
CC202408		0.08	0.81	0.99	10.7	<0.2	<10	2750	0.80	0.14	1.09	1.34	24.60	8.8	20	0.44
CC202409		0.02	NSS	NSS	NSS	NSS	NSS	NSS	NSS	NSS	NSS	NSS	NSS	NSS	NSS	NSS
CC202410		0.02	NSS	NSS	NSS	NSS	NSS	NSS	NSS	NSS	NSS	NSS	NSS	NSS	NSS	NSS

Comments: Interference: Ca>10% on ICP-MS As,ICP-AES results shown. Gold determinations by ME-MS41 are semi-quantitative due to the small sample weight used (0.5g). NSS is non-sufficient sample.

ALS Chemex

EXCELLENCE IN ANALYTICAL CHEMISTRY

ALS Canada Ltd.

212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: STRATEGIC METALS LTD.
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO

Finalized Date: 25-JUN-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07060639

Sample Description	Method	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41
	Analyte	Cu	Fe	Ga	Ge	Hf	Hg	In	K	La	Li	Mg	Mn	Mo	Na	Nb
	Units	ppm	%	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	%	ppm	ppm	%	ppm
	LOR	0.2	0.01	0.05	0.05	0.02	0.01	0.005	0.01	0.2	0.1	0.01	5	0.05	0.01	0.05
CC202352		9.6	0.43	0.39	<0.05	0.02	0.14	<0.005	0.05	1.3	0.5	0.10	1075	2.29	0.04	0.06
CC202353		18.0	3.12	3.26	0.08	0.07	0.12	0.019	0.06	9.5	10.8	0.41	2820	2.75	0.02	0.44
CC202354		13.1	7.10	1.83	0.10	0.07	0.13	0.007	0.02	2.9	0.5	0.04	20200	8.37	0.23	0.12
CC202355		11.7	3.81	1.70	0.07	0.05	0.10	0.007	0.02	2.7	0.4	0.03	16500	4.10	0.51	0.10
CC202356		5.7	0.34	0.31	<0.05	<0.02	0.10	<0.005	0.08	0.6	0.1	0.14	124	8.65	0.03	0.06
CC202357		4.9	0.93	0.34	<0.05	0.02	0.07	<0.005	0.04	1.2	0.1	0.12	50	1.51	0.58	<0.05
CC202358		5.9	0.31	0.25	<0.05	<0.02	0.14	<0.005	0.09	0.7	0.1	0.13	134	2.60	0.03	<0.05
CC202359		5.8	0.44	0.28	<0.05	<0.02	0.16	<0.005	0.05	0.9	0.1	0.11	59	1.57	0.21	<0.05
CC202360		5.3	1.10	0.87	<0.05	0.02	0.08	<0.005	0.04	2.4	0.8	0.08	18	2.25	0.41	0.12
CC202361		23.3	3.53	3.97	0.11	0.11	0.10	0.031	0.09	21.3	15.5	0.57	638	4.90	0.02	0.48
CC202362		17.7	1.91	3.06	0.08	0.06	0.13	0.021	0.08	11.5	7.1	0.21	99	1.90	0.02	0.42
CC202363		25.6	2.17	4.43	0.10	0.09	0.10	0.029	0.10	18.1	14.3	0.50	120	2.99	0.02	0.55
CC202364		18.8	2.08	4.96	0.08	0.05	0.11	0.027	0.07	14.1	11.4	0.31	75	0.97	0.01	0.66
CC202365		17.6	0.47	0.36	<0.05	0.05	0.12	0.007	0.05	1.4	0.8	0.23	139	7.95	0.21	0.07
CC202366		67.0	2.23	2.83	0.13	0.11	0.19	0.030	0.12	16.3	8.9	0.41	175	21.40	0.01	0.30
CC202367		131.0	4.90	3.57	0.21	0.16	0.43	0.074	0.35	16.8	10.7	0.84	207	61.10	0.03	0.30
CC202368		34.0	1.49	2.33	0.08	0.06	0.12	0.026	0.10	8.4	2.4	0.09	51	37.10	0.01	0.22
CC202369		92.8	1.64	2.96	0.13	0.17	0.59	0.034	0.10	15.4	3.3	0.10	113	31.40	0.02	0.26
CC202370		41.4	1.55	2.35	0.12	0.21	0.40	0.026	0.10	8.4	2.8	0.11	140	25.30	0.02	0.33
CC202371		34.3	2.83	3.46	0.09	0.03	0.06	0.034	0.13	8.4	1.2	0.05	72	52.30	0.01	0.33
CC202372		32.9	2.95	2.36	0.11	0.04	0.05	0.033	0.13	7.2	0.9	0.04	81	50.10	0.02	0.22
CC202373		38.4	3.21	2.57	0.14	0.04	0.06	0.035	0.13	8.3	1.4	0.05	135	62.60	0.03	0.27
CC202374		24.7	1.59	4.82	0.08	0.12	0.11	0.029	0.08	18.0	16.7	0.58	469	1.66	0.02	0.69
CC202375		43.5	3.74	2.40	0.17	0.12	0.09	0.041	0.19	10.1	2.1	0.07	198	57.30	0.05	0.29
CC202395		32.5	2.29	3.95	0.09	0.13	0.10	0.024	0.08	16.5	14.6	0.59	631	2.88	0.02	0.63
CC202396		23.1	1.99	3.95	0.09	0.14	0.09	0.022	0.09	15.4	15.1	0.76	263	3.75	0.03	0.67
CC202397		82.3	2.21	2.94	0.13	0.16	0.18	0.031	0.16	10.4	9.9	0.40	122	50.50	0.01	0.19
CC202398		NSS	NSS	NSS	NSS	NSS	NSS	NSS	NSS	NSS	NSS	NSS	NSS	NSS	NSS	NSS
CC202399		19.2	1.54	3.39	0.07	0.08	0.13	0.020	0.06	12.8	11.1	0.47	255	2.62	0.02	0.47
CC202400		22.8	1.61	3.45	0.08	0.12	0.11	0.021	0.07	13.4	11.8	0.55	271	3.53	0.02	0.51
CC202401		17.2	2.66	5.09	0.11	0.06	0.04	0.053	0.08	4.8	9.7	0.08	51	79.80	0.01	0.74
CC202402		43.2	2.85	5.71	0.15	0.02	0.08	0.051	0.08	5.2	1.0	0.03	31	95.80	0.01	0.26
CC202403		16.7	4.23	8.09	0.11	0.06	0.07	0.040	0.09	9.6	11.3	0.22	146	24.70	0.01	1.30
CC202404		55.2	4.11	5.68	0.17	0.15	0.14	0.050	0.10	13.3	14.4	0.37	286	22.10	0.02	0.89
CC202405		41.8	3.98	5.25	0.21	0.11	0.11	0.054	0.14	10.2	11.1	0.20	278	65.30	0.02	1.00
CC202406		10.5	1.97	5.29	0.07	<0.02	0.05	0.020	0.08	10.5	3.9	0.14	104	18.20	0.01	0.73
CC202407		50.3	2.13	1.36	0.12	0.07	0.14	0.022	0.09	9.8	2.2	0.10	240	10.05	0.02	0.20
CC202408		32.3	2.58	2.60	0.11	0.12	0.16	0.032	0.11	12.9	5.4	0.25	223	9.09	0.01	0.30
CC202409		NSS	NSS	NSS	NSS	NSS	NSS	NSS	NSS	NSS	NSS	NSS	NSS	NSS	NSS	NSS
CC202410		NSS	NSS	NSS	NSS	NSS	NSS	NSS	NSS	NSS	NSS	NSS	NSS	NSS	NSS	NSS

Comments: Interference: Ca>10% on ICP-MS As,ICP-AES results shown. Gold determinations by ME-MS41 are semi-quantitative due to the small sample weight used (0.5g). NSS is non-sufficient sample.

ALS Chemex

EXCELLENCE IN ANALYTICAL CHEMISTRY

ALS Canada Ltd.

212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: STRATEGIC METALS LTD.
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO

Finalized Date: 25-JUN-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07060639

Sample Description	Method	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41
	Analyte	Ni	P	Pb	Rb	Re	S	Sb	Sc	Se	Sn	Sr	Ta	Te	Th	Ti
	Units	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%
	LOR	0.2	10	0.2	0.1	0.001	0.01	0.05	0.1	0.2	0.2	0.2	0.01	0.01	0.2	0.005
CC202352		7.6	810	3.1	2.6	0.001	0.18	0.62	0.4	1.2	<0.2	67.3	0.01	0.02	<0.2	<0.005
CC202353		23.8	1390	8.0	6.5	0.001	0.14	1.46	2.4	2.0	0.3	55.2	<0.01	0.05	1.3	0.014
CC202354		21.6	1460	2.0	1.4	0.002	0.40	0.78	1.0	2.0	<0.2	58.1	<0.01	0.05	0.3	<0.005
CC202355		21.4	1090	1.4	0.9	0.002	0.65	0.62	1.3	2.0	<0.2	50.6	<0.01	0.04	0.3	<0.005
CC202356		4.0	760	1.0	1.2	0.001	0.13	0.19	0.3	0.7	<0.2	37.1	0.06	0.01	<0.2	<0.005
CC202357		5.9	1050	1.1	0.8	0.001	0.65	0.31	1.1	1.1	<0.2	42.6	0.03	0.02	<0.2	<0.005
CC202358		4.0	1000	1.2	2.2	0.001	0.12	0.19	0.2	0.8	<0.2	38.2	0.03	0.01	<0.2	<0.005
CC202359		4.6	840	1.6	1.5	0.001	0.28	0.42	0.6	0.8	<0.2	37.4	0.03	0.01	<0.2	<0.005
CC202360		4.3	910	1.9	2.4	0.001	0.50	0.32	1.6	1.4	<0.2	22.3	0.02	0.02	0.4	<0.005
CC202361		29.7	1440	9.6	9.6	0.004	0.09	1.88	5.1	3.2	0.4	36.3	0.01	0.05	3.3	0.013
CC202362		12.3	670	8.1	9.1	0.003	0.07	0.84	3.0	3.2	0.3	12.8	0.01	0.03	2.3	0.009
CC202363		21.8	1070	10.9	11.9	0.002	0.05	1.52	4.4	2.9	0.5	40.6	<0.01	0.04	3.5	0.012
CC202364		11.6	480	10.2	8.4	0.005	0.05	0.92	3.8	3.4	0.5	12.6	<0.01	0.05	3.2	0.012
CC202365		32.2	1120	1.9	2.8	0.003	0.46	1.33	0.9	7.2	<0.2	89.3	0.03	0.03	0.3	<0.005
CC202366		205.0	1060	9.8	10.1	0.018	0.18	3.61	4.7	7.4	0.4	48.9	0.01	0.06	3.1	0.007
CC202367		230.0	1660	16.2	18.6	0.015	0.89	8.95	7.1	16.9	0.8	129.5	0.01	0.15	4.6	0.006
CC202368		35.9	320	8.3	9.4	0.011	0.08	3.74	3.3	6.0	0.4	35.2	<0.01	0.08	2.1	0.006
CC202369		233.0	840	10.9	10.4	0.014	0.13	8.91	5.0	10.8	0.7	70.9	0.01	0.16	2.2	0.005
CC202370		134.5	800	8.2	9.4	0.009	0.25	9.50	4.0	13.8	0.5	84.7	0.02	0.11	1.3	0.006
CC202371		78.5	410	12.8	11.6	0.003	0.21	5.53	2.6	8.5	0.7	32.2	<0.01	0.12	1.8	0.007
CC202372		91.5	470	12.9	11.4	0.004	0.28	5.48	2.8	12.2	0.5	32.8	<0.01	0.11	1.9	<0.005
CC202373		118.5	610	13.1	10.1	0.005	0.36	7.16	3.0	18.3	0.6	39.2	<0.01	0.16	1.5	0.007
CC202374		21.6	1530	11.2	10.5	0.002	0.09	1.36	4.7	2.5	0.5	40.9	<0.01	0.05	3.6	0.017
CC202375		135.0	580	13.4	11.6	0.007	0.53	6.70	4.8	19.1	0.4	61.1	<0.01	0.17	3.5	0.009
CC202395		26.2	1180	10.1	8.5	0.001	0.09	1.75	4.0	2.3	0.4	57.1	<0.01	0.06	2.4	0.019
CC202396		21.6	1520	9.0	8.7	0.001	0.10	1.75	4.1	2.2	0.4	60.3	0.01	0.04	2.6	0.022
CC202397		249.0	810	9.5	9.4	0.009	0.07	7.08	5.4	7.0	0.5	53.2	0.01	0.13	2.4	<0.005
CC202398		NSS	NSS	NSS	NSS	NSS	NSS	NSS	NSS	NSS	NSS	NSS	NSS	NSS	NSS	NSS
CC202399		17.9	1190	7.4	6.1	0.001	0.11	1.30	3.1	2.4	0.3	53.6	0.01	0.05	1.4	0.014
CC202400		21.8	1230	7.3	6.9	0.001	0.11	1.61	3.3	2.5	0.4	61.8	0.01	0.04	1.5	0.013
CC202401		6.6	400	10.2	11.3	0.002	0.10	12.40	2.8	17.7	0.7	27.3	<0.01	0.16	2.1	0.018
CC202402		21.5	670	13.7	7.8	0.002	0.13	22.70	2.4	24.8	1.0	25.7	<0.01	0.40	0.8	0.009
CC202403		13.8	400	11.7	14.0	<0.001	0.05	5.75	3.1	8.2	0.9	16.8	<0.01	0.16	3.0	0.031
CC202404		178.0	910	12.9	11.6	0.001	0.14	7.38	5.6	16.3	0.8	60.3	0.01	0.15	3.6	0.014
CC202405		76.0	680	14.5	12.7	0.004	0.25	15.85	4.5	34.6	0.8	83.6	<0.01	0.25	4.0	0.025
CC202406		21.0	260	9.5	13.2	0.001	0.03	2.55	2.1	4.1	0.7	12.3	<0.01	0.07	1.7	0.023
CC202407		133.5	1180	7.8	5.3	0.004	0.09	4.07	2.9	9.7	0.3	39.7	0.01	0.07	1.3	0.007
CC202408		41.4	660	10.6	8.1	0.002	0.06	3.08	5.0	2.8	0.4	47.5	0.01	0.07	2.7	0.007
CC202409		NSS	NSS	NSS	NSS	NSS	NSS	NSS	NSS	NSS	NSS	NSS	NSS	NSS	NSS	NSS
CC202410		NSS	NSS	NSS	NSS	NSS	NSS	NSS	NSS	NSS	NSS	NSS	NSS	NSS	NSS	NSS

Comments: Interference: Ca>10% on ICP-MS As,ICP-AES results shown. Gold determinations by ME-MS41 are semi-quantitative due to the small sample weight used (0.5g). NSS is non-sufficient sample.

ALS Chemex

EXCELLENCE IN ANALYTICAL CHEMISTRY

ALS Canada Ltd.

212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: STRATEGIC METALS LTD.
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO

Finalized Date: 25-JUN-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07060639

Sample Description	Method	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41
	Analyte	Tl	U	V	W	Y	Zn	Zr
	Units	ppm	ppm	ppm	ppm	ppm	ppm	ppm
	LOR	0.02	0.05	1	0.05	0.05	2	0.5
CC202352		0.05	0.26	5	0.08	2.94	60	0.5
CC202353		0.11	1.63	70	0.14	10.25	167	1.6
CC202354		0.22	0.58	22	0.12	9.27	208	1.3
CC202355		0.14	0.88	18	0.07	8.37	166	1.1
CC202356		<0.02	0.05	2	0.08	1.37	36	<0.5
CC202357		<0.02	0.20	3	0.07	2.33	32	<0.5
CC202358		<0.02	0.05	3	0.07	1.55	50	<0.5
CC202359		<0.02	0.08	3	0.06	1.82	31	<0.5
CC202360		0.03	0.46	10	0.07	1.97	19	0.7
CC202361		0.16	2.48	111	0.25	20.80	191	2.2
CC202362		0.13	1.47	48	0.10	7.08	66	1.4
CC202363		0.20	1.98	95	0.14	12.95	125	2.0
CC202364		0.27	1.76	92	0.11	6.40	79	1.3
CC202365		0.39	0.86	21	0.08	2.98	121	1.2
CC202366		1.41	4.90	115	0.14	29.80	738	2.0
CC202367		6.03	11.10	210	0.24	33.70	554	4.0
CC202368		1.43	3.94	194	0.12	10.55	169	1.5
CC202369		1.41	10.65	384	0.25	31.60	971	5.1
CC202370		2.34	6.94	224	0.20	23.30	697	6.1
CC202371		2.19	2.65	264	0.17	7.30	171	0.7
CC202372		2.64	2.05	229	0.15	9.41	194	1.1
CC202373		3.44	2.71	225	0.20	14.60	245	0.6
CC202374		0.19	2.06	97	0.12	13.65	124	2.7
CC202375		4.17	2.63	200	0.17	15.00	265	4.1
CC202395		0.14	1.78	95	0.18	14.10	135	2.8
CC202396		0.14	1.57	96	0.13	11.65	159	3.1
CC202397		1.06	2.83	310	0.19	28.30	682	3.8
CC202398		NSS	NSS	NSS	NSS	NSS	NSS	NSS
CC202399		0.12	2.10	80	0.11	10.00	108	1.8
CC202400		0.16	1.23	72	0.12	11.60	129	2.7
CC202401		2.50	2.03	303	0.33	3.54	33	1.9
CC202402		3.24	4.07	660	0.50	4.76	58	<0.5
CC202403		1.28	1.05	238	0.23	2.51	63	2.0
CC202404		1.30	3.10	310	0.40	26.90	670	3.0
CC202405		4.67	1.89	226	0.32	8.67	224	3.8
CC202406		0.82	0.55	162	0.17	2.54	81	<0.5
CC202407		0.28	2.92	96	0.12	19.80	379	1.7
CC202408		0.15	2.06	94	0.12	18.15	204	2.3
CC202409		NSS	NSS	NSS	NSS	NSS	NSS	NSS
CC202410		NSS	NSS	NSS	NSS	NSS	NSS	NSS

Comments: Interference: Ca>10% on ICP-MS As,ICP-AES results shown. Gold determinations by ME-MS41 are semi-quantitative due to the small sample weight used (0.5g). NSS is non-sufficient sample.

ALS Chemex

EXCELLENCE IN ANALYTICAL CHEMISTRY

ALS Canada Ltd.

212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: STRATEGIC METALS LTD.
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Finalized Date: 25-JUN-2007
Account: MTT

Project: NIMO

CERTIFICATE OF ANALYSIS VA07060639

Sample Description	Method	WEI-21	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41
	Analyte	Recvd Wt.	Ag	Al	As	Au	B	Ba	Be	Bi	Ca	Cd	Ce	Co	Cr	Cs
	Units	kg	ppm	%	ppm	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppm	ppm	ppm
	LOR	0.02	0.01	0.01	0.1	0.2	10	10	0.05	0.01	0.01	0.01	0.02	0.1	1	0.05
CC202411		0.04	0.84	0.41	4.4	<0.2	<10	870	0.35	0.11	0.24	1.04	10.95	4.1	8	0.58
CC202412		0.02	0.80	0.51	1.9	<0.2	<10	1180	0.19	0.08	0.56	0.50	8.77	2.9	9	0.44
CC202413		0.02	NSS	NSS	NSS	NSS	NSS	NSS	NSS	NSS	NSS	NSS	NSS	NSS	NSS	NSS
CC202414		0.04	0.65	0.91	4.5	<0.2	<10	1320	0.33	0.15	0.21	0.39	14.40	5.0	16	0.46
CC202415		0.02	NSS	NSS	NSS	NSS	NSS	NSS	NSS	NSS	NSS	NSS	NSS	NSS	NSS	NSS
CC202416		0.02	0.09	0.04	0.8	<0.2	<10	300	<0.05	0.02	0.88	0.27	0.52	0.5	1	0.06
CC202417		0.06	0.35	0.21	0.9	<0.2	<10	1530	0.10	0.04	2.22	0.19	4.30	5.5	3	0.24
CC202418		0.02	0.13	0.26	1.6	<0.2	<10	1160	0.20	0.03	2.25	1.02	8.09	8.2	2	0.08
CC202419		0.02	0.56	0.33	1.4	<0.2	<10	960	0.26	0.05	1.89	1.85	8.39	2.7	4	0.58
CC202420		0.02	0.09	0.14	0.8	<0.2	10	760	0.11	0.02	3.19	3.10	3.38	1.6	2	0.21
CC202421		0.06	0.55	0.90	5.7	<0.2	<10	1970	0.50	0.15	1.77	0.96	19.70	7.5	15	0.47
CC202422		0.04	0.16	0.23	1.0	<0.2	10	1360	0.28	0.04	3.65	2.80	7.64	2.2	3	0.23
CC202423		0.06	0.42	0.91	4.8	<0.2	<10	1750	0.31	0.14	2.12	1.83	11.70	6.6	15	0.47
CC202424		0.04	0.14	0.15	0.8	<0.2	10	930	0.15	0.03	2.41	1.33	3.76	1.2	2	0.10
CC202425		0.06	0.39	0.64	3.9	<0.2	10	1780	0.31	0.08	3.35	2.05	8.10	3.8	11	0.33
CC202426		0.04	0.09	0.13	1.2	<0.2	10	930	0.09	0.03	4.45	2.84	1.77	1.0	2	0.17
CC202427		0.02	NSS	NSS	NSS	NSS	NSS	NSS	NSS	NSS	NSS	NSS	NSS	NSS	NSS	NSS
CC202428		0.16	0.13	2.38	15.7	<0.2	<10	300	0.46	0.25	0.06	0.50	21.30	8.3	36	1.42
CC20295		0.18	0.58	1.12	10.9	<0.2	<10	3240	0.62	0.19	0.30	0.37	22.10	13.1	24	0.68
CC20296		0.12	1.12	0.65	4.7	<0.2	10	3820	0.55	0.07	1.55	3.19	24.70	4.8	7	0.35
CC20297		0.14	0.72	0.34	5.0	<0.2	<10	1060	0.24	0.05	3.37	25.20	5.12	3.0	12	0.25
CC20298		0.18	2.14	0.88	80.3	<0.2	10	1290	0.74	0.27	0.45	39.40	30.70	10.0	41	1.02
CC20448		0.10	0.23	0.62	24.4	<0.2	<10	750	0.23	0.20	0.06	0.67	12.60	1.8	21	1.09
CC20449		0.06	0.40	0.68	34.0	<0.2	<10	740	0.31	0.25	0.13	0.82	13.05	1.8	22	0.84
CC20450		0.06	0.39	0.65	18.5	<0.2	<10	460	0.21	0.18	0.11	0.53	10.75	1.1	17	0.86

Comments: Interference: Ca>10% on ICP-MS As,ICP-AES results shown. Gold determinations by ME-MS41 are semi-quantitative due to the small sample weight used (0.5g). NSS is non-sufficient sample.

ALS Chemex

EXCELLENCE IN ANALYTICAL CHEMISTRY

ALS Canada Ltd.

212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: STRATEGIC METALS LTD.
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO

Finalized Date: 25-JUN-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07060639

Sample Description	Method	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41
	Analyte	Cu	Fe	Ga	Ge	Hf	Hg	In	K	La	Li	Mg	Mn	Mo	Na	Nb
	Units	ppm	%	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	%	ppm	ppm	%	ppm
	LOR	0.2	0.01	0.05	0.05	0.02	0.01	0.005	0.01	0.2	0.1	0.01	5	0.05	0.01	0.05
CC202411		36.7	1.04	1.59	<0.05	0.02	0.07	0.017	0.07	6.1	1.3	0.06	33	1.62	0.01	0.20
CC202412		16.1	0.92	1.88	<0.05	0.03	0.15	0.012	0.05	4.8	1.7	0.10	56	2.49	0.02	0.21
CC202413		NSS	NSS	NSS	NSS	NSS	NSS	NSS	NSS	NSS	NSS	NSS	NSS	NSS	NSS	NSS
CC202414		24.6	2.01	2.82	0.05	0.04	0.09	0.021	0.08	7.5	5.4	0.15	77	1.19	0.01	0.31
CC202415		NSS	NSS	NSS	NSS	NSS	NSS	NSS	NSS	NSS	NSS	NSS	NSS	NSS	NSS	NSS
CC202416		4.2	0.08	0.11	<0.05	<0.02	0.10	<0.005	0.03	0.3	0.1	0.10	25	2.93	0.21	<0.05
CC202417		9.7	0.49	0.56	<0.05	0.03	0.09	0.006	0.02	2.2	0.5	0.18	342	1.42	0.37	0.08
CC202418		13.0	0.36	0.32	<0.05	0.04	0.11	0.006	0.03	4.0	0.3	0.09	466	1.21	0.26	0.05
CC202419		17.5	0.51	0.89	<0.05	0.04	0.10	0.008	0.04	4.7	1.3	0.09	87	1.86	0.32	0.12
CC202420		13.2	0.24	0.31	<0.05	0.04	0.10	<0.005	0.05	1.9	0.6	0.12	221	1.73	0.22	0.06
CC202421		32.3	1.83	2.42	0.06	0.11	0.10	0.024	0.07	10.5	6.6	0.24	390	2.64	0.06	0.30
CC202422		24.7	0.37	0.53	<0.05	0.06	0.09	0.006	0.03	5.7	1.2	0.14	307	1.00	0.37	0.08
CC202423		18.0	1.66	2.70	<0.05	0.08	0.09	0.023	0.07	5.9	6.4	0.23	363	2.43	0.02	0.32
CC202424		19.5	0.25	0.29	<0.05	0.04	0.12	<0.005	0.04	2.7	0.5	0.14	165	1.41	0.40	0.05
CC202425		24.4	1.10	1.70	<0.05	0.09	0.12	0.017	0.05	4.4	3.8	0.29	189	2.18	0.02	0.23
CC202426		13.8	0.21	0.30	<0.05	0.04	0.10	<0.005	0.02	1.1	0.6	0.32	316	0.77	0.24	0.06
CC202427		NSS	NSS	NSS	NSS	NSS	NSS	NSS	NSS	NSS	NSS	NSS	NSS	NSS	NSS	NSS
CC202428		27.0	3.88	6.26	0.07	0.08	0.05	0.041	0.09	11.4	23.1	0.41	203	8.71	0.01	0.99
CC20295		39.8	4.85	2.88	0.09	0.06	0.19	0.037	0.10	11.6	6.3	0.17	453	2.69	0.01	0.34
CC20296		25.6	0.90	1.19	0.07	0.06	0.18	0.014	0.04	13.9	1.3	0.21	94	1.53	0.11	0.16
CC20297		41.5	0.43	0.83	0.06	0.09	0.25	0.009	0.02	3.3	1.1	0.17	156	3.25	0.44	0.13
CC20298		120.0	2.85	3.46	0.12	0.07	0.96	0.044	0.13	16.9	5.0	0.12	173	81.40	0.01	0.26
CC20448		20.4	1.76	5.36	0.05	<0.02	0.07	0.033	0.09	6.9	1.1	0.04	42	41.50	0.01	0.39
CC20449		30.7	1.97	5.12	0.06	<0.02	0.08	0.039	0.11	7.1	1.3	0.06	55	45.20	0.01	0.39
CC20450		20.2	1.17	4.49	<0.05	0.02	0.06	0.018	0.07	6.2	1.1	0.05	20	28.90	0.01	0.33

Comments: Interference: Ca>10% on ICP-MS As,ICP-AES results shown. Gold determinations by ME-MS41 are semi-quantitative due to the small sample weight used (0.5g). NSS is non-sufficient sample.

ALS Chemex
EXCELLENCE IN ANALYTICAL CHEMISTRY
ALS Canada Ltd.
212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: STRATEGIC METALS LTD.
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO

Finalized Date: 25-JUN-2007
Account: MTT

CERTIFICATE OF ANALYSIS VA07060639

Sample Description	Method	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41
	Analyte	Ni	P	Pb	Rb	Re	S	Sb	Sc	Se	Sn	Sr	Ta	Te	Th	Ti
	Units	ppm	ppm	ppm	ppm	ppm	%	ppm	ppm	ppm	ppm	ppm	ppm	ppm	ppm	%
	LOR	0.2	10	0.2	0.1	0.001	0.01	0.05	0.1	0.2	0.2	0.2	0.01	0.01	0.2	0.005
CC202411		25.8	1110	7.2	6.6	0.001	0.08	0.95	1.2	2.0	0.2	31.8	<0.01	0.05	0.4	0.005
CC202412		13.7	1350	4.0	4.6	0.001	0.13	0.62	1.8	2.1	0.2	36.1	0.01	0.04	0.7	<0.005
CC202413		NSS	NSS	NSS	NSS	NSS	NSS	NSS	NSS	NSS	NSS	NSS	NSS	NSS	NSS	NSS
CC202414		15.5	640	7.2	7.6	0.002	0.05	0.60	2.4	1.6	0.3	18.8	<0.01	0.05	2.1	0.005
CC202415		NSS	NSS	NSS	NSS	NSS	NSS	NSS	NSS	NSS	NSS	NSS	NSS	NSS	NSS	NSS
CC202416		2.1	640	0.8	1.1	0.001	0.29	0.35	0.4	0.8	<0.2	56.2	<0.01	0.01	<0.2	<0.005
CC202417		10.5	910	2.1	1.6	0.003	0.48	0.70	1.3	1.9	<0.2	141.0	<0.01	0.02	0.2	<0.005
CC202418		9.4	880	1.6	1.7	0.001	0.33	1.30	0.9	1.2	<0.2	85.9	<0.01	0.02	0.2	<0.005
CC202419		11.1	800	4.1	6.1	<0.001	0.40	0.60	1.7	1.2	<0.2	65.4	<0.01	0.02	0.4	0.005
CC202420		7.8	890	1.1	3.5	0.002	0.34	1.00	0.8	1.2	<0.2	91.7	<0.01	0.02	0.2	<0.005
CC202421		31.0	900	7.9	7.5	0.002	0.12	1.30	3.2	2.5	0.2	63.1	<0.01	0.05	1.9	0.007
CC202422		23.9	840	2.4	3.1	0.001	0.47	0.60	1.5	1.6	<0.2	107.0	<0.01	0.02	0.4	<0.005
CC202423		20.2	940	7.9	11.7	0.001	0.09	1.08	2.9	1.8	0.3	67.4	<0.01	0.05	1.3	0.007
CC202424		19.2	890	1.3	2.3	0.005	0.49	0.76	1.1	1.5	<0.2	79.1	<0.01	0.02	0.2	<0.005
CC202425		30.5	860	4.1	5.3	0.002	0.15	1.32	2.2	2.6	0.2	129.0	<0.01	0.04	0.9	0.005
CC202426		14.8	750	1.8	1.4	0.003	0.38	0.69	0.7	1.8	<0.2	145.5	<0.01	0.02	0.2	<0.005
CC202427		NSS	NSS	NSS	NSS	NSS	NSS	NSS	NSS	NSS	NSS	NSS	NSS	NSS	NSS	NSS
CC202428		39.7	270	15.6	15.4	<0.001	<0.01	1.85	4.3	1.7	0.7	12.5	<0.01	0.07	4.1	0.021
CC20295		38.9	580	9.5	10.6	0.002	0.03	1.05	5.6	2.0	0.3	23.4	<0.01	0.05	2.9	0.007
CC20296		27.6	1000	6.7	2.9	0.004	0.22	1.27	2.8	3.9	<0.2	113.0	0.01	0.03	0.7	0.007
CC20297		84.2	1000	3.2	1.7	0.004	0.56	3.44	2.1	7.7	<0.2	147.0	0.01	0.05	0.3	0.005
CC20298		302.0	620	14.7	13.1	0.003	0.03	31.60	6.7	6.3	0.8	38.1	0.01	0.20	3.1	0.010
CC20448		22.0	660	11.2	9.1	0.002	0.14	5.68	1.8	5.0	0.7	25.8	<0.01	0.14	0.4	0.011
CC20449		23.9	810	13.1	10.5	0.002	0.18	5.92	2.0	5.6	0.8	36.8	<0.01	0.17	0.4	0.010
CC20450		20.6	410	11.5	9.5	0.003	0.06	5.19	1.8	4.2	0.7	27.1	<0.01	0.12	1.4	0.009

Comments: Interference: Ca>10% on ICP-MS As,ICP-AES results shown. Gold determinations by ME-MS41 are semi-quantitative due to the small sample weight used (0.5g). NSS is non-sufficient sample.

ALS Chemex
EXCELLENCE IN ANALYTICAL CHEMISTRY
ALS Canada Ltd.
212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: STRATEGIC METALS LTD.
C/O ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016-510 W HASTINGS ST
VANCOUVER BC V6B 1L8

Project: NIMO

CERTIFICATE OF ANALYSIS VA07060639

Sample Description	Method	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41	ME-MS41
	Analyte	Tl	U	V	W	Y	Zn	Zr
	Units	ppm	ppm	ppm	ppm	ppm	ppm	ppm
	LOR	0.02	0.05	1	0.05	0.05	2	0.5
CC202411		0.07	0.81	23	0.09	6.10	87	<0.5
CC202412		0.07	0.86	21	0.06	5.42	46	0.7
CC202413		NSS	NSS	NSS	NSS	NSS	NSS	NSS
CC202414		0.07	0.59	34	0.07	6.03	69	1.0
CC202415		NSS	NSS	NSS	NSS	NSS	NSS	NSS
CC202416		<0.02	<0.05	1	<0.05	0.28	24	<0.5
CC202417		0.03	0.25	6	<0.05	3.23	11	1.0
CC202418		0.02	0.29	3	<0.05	6.25	38	0.9
CC202419		0.03	0.40	9	<0.05	5.42	43	1.2
CC202420		0.02	0.17	3	<0.05	2.69	70	1.1
CC202421		0.07	1.39	37	0.07	11.70	110	2.8
CC202422		0.03	0.32	6	<0.05	7.65	76	1.7
CC202423		0.09	1.03	43	0.05	4.30	131	1.9
CC202424		0.02	0.33	4	<0.05	5.28	51	1.1
CC202425		0.07	2.02	37	0.05	4.85	144	2.7
CC202426		0.03	0.55	4	<0.05	1.49	156	1.3
CC202427		NSS	NSS	NSS	NSS	NSS	NSS	NSS
CC202428		0.53	0.81	115	0.16	3.45	153	3.1
CC20295		0.14	1.37	42	0.08	16.60	116	1.5
CC20296		0.05	2.00	20	0.06	21.10	62	1.5
CC20297		0.17	7.59	155	0.06	8.13	376	3.4
CC20298		1.36	4.24	754	0.25	32.80	1730	1.5
CC20448		1.69	1.78	255	0.23	3.06	73	<0.5
CC20449		2.17	2.22	253	0.25	3.23	76	<0.5
CC20450		1.42	2.08	233	0.19	2.48	52	0.8

Comments: Interference: Ca>10% on ICP-MS As,ICP-AES results shown. Gold determinations by ME-MS41 are semi-quantitative due to the small sample weight used (0.5g). NSS is non-sufficient sample.

APPENDIX III

ROCK SAMPLE DESCRIPTIONS

Rock Sample Descriptions

Project: _____ Property: _____

Sample Number: C385613 | Grid North: UTM: 444403 N | Grid East: UTM: 7357136 E | Type: chip | Sample Width: 3.5 cm | Dimension: | Abundance: | Elevation: m

Comments: Crumbly black material with pieces up to 1cm × 2cm × 3cm

Sample Number: C385614 | Grid North: UTM: 444403 N | Grid East: UTM: 7357136 E | Type: specimen sample | Sample Width: 33 cm | Dimension: | Abundance: | Elevation: m

↑ 20m down slope

Comments: limestone cluster 6cm × 10cm × 2cm coated w ~~limonite~~ intense limonite crystals on the outside and in voids

Sample Number: C385615 | Grid North: UTM: 444403 N | Grid East: UTM: 7357136 E | Type: specimen sample | Sample Width: | Dimension: | Abundance: | Elevation: m

↑ bottom slope

Comments: crumbly black material. Bituminous w pieces up to 3cm × 2cm × 1cm. Thought to be weathered NiMo horizon

Sample Number: C385616 | Grid North: West of outcrop UTM: 444437 N | Grid East: UTM: 7357049 E | Type: chip | Sample Width: | Dimension: | Abundance: | Elevation: m

Comments: 5cm thick NiMo; brecciated dark grey fine grained bitumen horizon w heavy weight & sulphur smell No reaction w HCl

Sample Number: C385617 | Grid North: West of outcrop UTM: 444437 N | Grid East: UTM: 7357049. E | Type: chip | Sample Width: | Dimension: | Abundance: | Elevation: m

Comments: Black crumbly material w pieces same as C385616 (~ 20% these pieces) no rxn w HCl

Sample Number: C385618 | Grid North: btwn C385616 & C385617 UTM: N | Grid East: UTM: E | Type: specimen | Sample Width: | Dimension: | Abundance: | Elevation: m

Comments: white precipitate found on rock btwn C385616 & C385617 thought to be gypsum

Rock Sample Descriptions

Project: NiMo Property: Rich

Sample Number: C385619 Grid North: UTM: Elevation: N Grid East: UTM: N E Type: chip E Sample Width: 1.5cm Dimension: Abundance:

Comments: Rusty layer fz from C385620 → C385623. Heavily limonite stn small fragment of black ? dark grey shale. Possible NiMo horizon.

Sample Number: C385620 Grid North: UTM: 443603 Elevation: N Grid East: UTM: 7358522 N E Type: chip E Sample Width: 0–15cm Dimension: Abundance:

Comments: Black v. calcareous rusty shale w botryoidal carbonate encrustation. Reacts strongly w HCl.

Sample Number: C385621 Grid North: UTM: 443603 Elevation: N Grid East: UTM: 7358522 N E Type: chip E Sample Width: 15cm – 29cm Dimension: Abundance:

Comments: V. well laminated limestone, lenticular layer. Sparks when hit w rock hammer slightly dense feeling. Reacts strongly w HCl. Porous & irregular

Sample Number: C385622 Grid North: UTM: 443603 Elevation: N Grid East: UTM: 7358522 N E Type: chip E Sample Width: 29 – 38cm Dimension: Abundance:

Comments: Reacts readily w HCl + v. effervescent (kuntocalcite?) black unit w white calcite fracture fillings.

Sample Number: C385623 Grid North: UTM: 443603 Elevation: N Grid East: (top) UTM: 7358522 N E Type: chip E Sample Width: 38–59cm Dimension: Abundance:

Comments: V. irregular fracturing w Mn stain. Reacts readily w HCl. Black & carbonaceous. Poorly laminated.

Sample Number: C385624 Grid North: UTM: 443468 Elevation: N Grid East: UTM: 7358513 N E Type: 1–1.5cm E Sample Width: 1–1.5cm Dimension: Abundance:

Comments: potential NiMo black crumbly weathered horizon. Sulphur smell v. friable w small flakes on rxn w HCl pieces 4mm x 4mm black chert

Rock Sample Descriptions

Project: NiMo Property: Rich

Sample Number: C385625 Grid North: UTM: 443468 N Grid East: UTM: 7358513 E Type: chip E Sample Width: 20-36cm Dimension: Abundance:
Elevation: m
Comments: Argillite black shale w/ 1cm x 3cm chert? nodules no reaction w/ HCl Yellow (oxidation products?) weathers light grey

Sample Number: C385626 Grid North: UTM: 443468 N Grid East: UTM: 7358513 ↑ across stream E Type: chip E Sample Width: 15cm Dimension: Abundance:
Elevation: m
Comments: The black material thought to be weathered NiMo horizon.

Sample Number: Grid North: N Grid East: E Type: Dimension:
UTM: N UTM: E Sample Width: Abundance:
Elevation: m
Comments:

Sample Number: Grid North: N Grid East: E Type: Dimension:
UTM: N UTM: E Sample Width: Abundance:
Elevation: m
Comments:

Sample Number: Grid North: N Grid East: E Type: Dimension:
UTM: N UTM: E Sample Width: Abundance:
Elevation: m
Comments:

Sample Number: Grid North: N Grid East: E Type: Dimension:
UTM: N UTM: E Sample Width: Abundance:
Elevation: m
Comments:

Rock Sample Descriptions — Project: NiMo — Property: Rich

Sample Number: C385634 — Grid East: UTM: 442070 E — Grid North: UTM: 7360580 N — Type: chip — Sample Width: 7cm — Dimension: — Abundance: — Elevation:

Comments: Black, fine grain gougy material thought to be weathered NiMo.

Sample Number: C385635 — Grid East: UTM: 442070 E — Grid North: UTM: 7360580 N — Type: chip — Sample Width: 30cm — Dimension: — Abundance: — Elevation:

Comments: fine grained dark grey recessive shale layer (NSM?), heavily limonized along fractures

Sample Number: C385636 — Grid East: UTM: 445580 E — Grid North: UTM: 7353452 N — Type: chip — Sample Width: 1-2cm — Dimension: — Abundance: — Elevation:

Comments: Fine grain dark grey bioturbated shale - NiMo horizon

Sample Number: C385637 — Grid East: UTM: 445580 E — Grid North: UTM: 7353452 N — Type: chip — Sample Width: — Dimension: — Abundance: — Elevation:

Comments: dark grey shale, heavily broken down (1mm → 2cm wide pieces) with a distinct sulpher smell

Sample Number: — Grid East: UTM: E — Grid North: UTM: N — Type: — Sample Width: — Dimension: — Abundance: — Elevation:

Comments:

Sample Number: — Grid East: UTM: E — Grid North: UTM: N — Type: — Sample Width: — Dimension: — Abundance: — Elevation:

Comments:

Archive Cathro Associates (1981) Limited

APPENDIX IV

GEOPHYSICAL REPORT

REPORT ON A HELICOPTER-BORNE VERSATILE TIME DOMAIN ELECTROMAGNETIC (VTEM) GEOPHYSICAL SURVEY

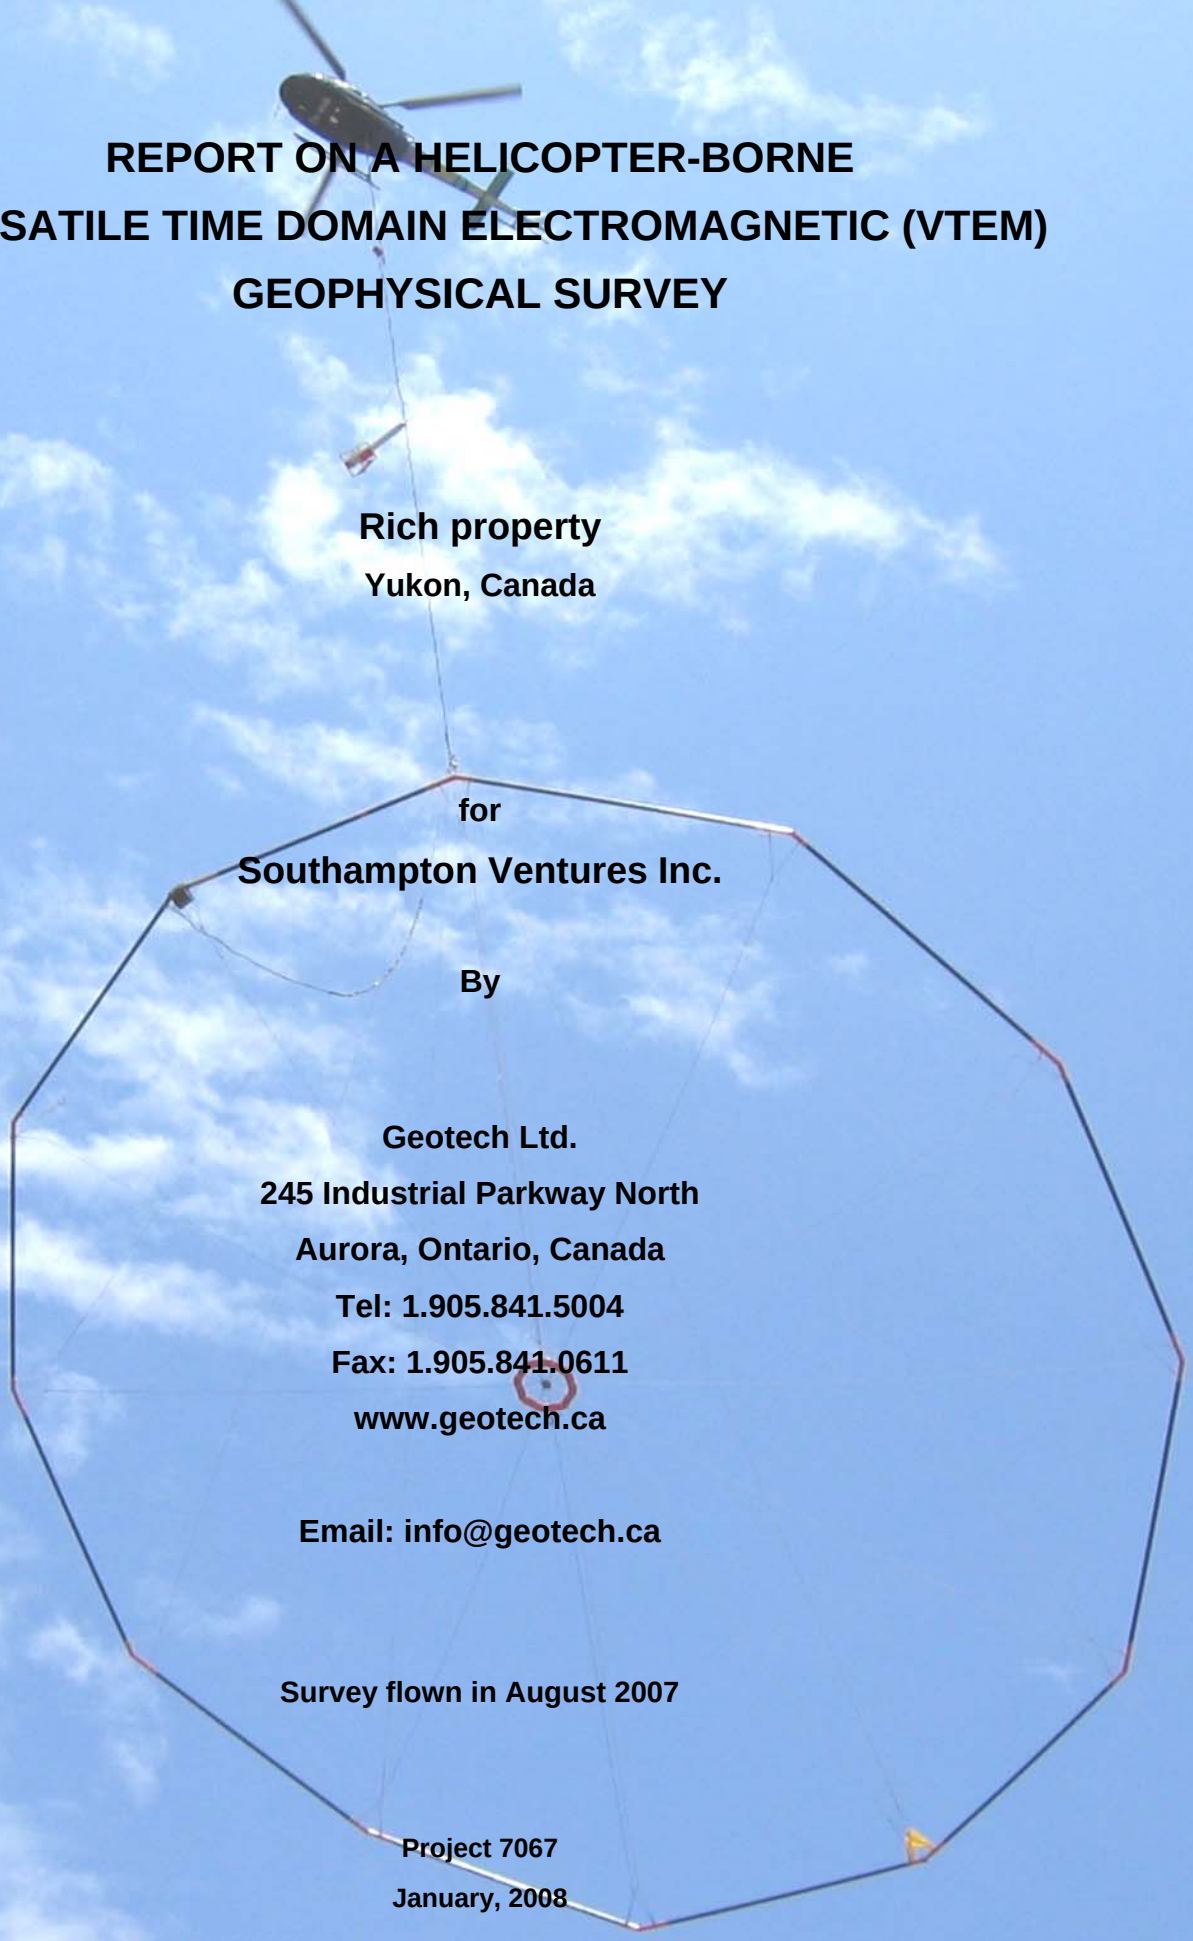

Rich property

Yukon, Canada

for

Southampton Ventures Inc.

By

Geotech Ltd.

245 Industrial Parkway North

Aurora, Ontario, Canada

Tel: 1.905.841.5004

Fax: 1.905.841.0611

www.geotech.ca

Email: info@geotech.ca

Survey flown in August 2007

Project 7067

January, 2008

TABLE OF CONTENTS

Executive Summary 3
1. INTRODUCTION 4
1.1 General Considerations 4
1.2. Survey and System Specifications 4
1.3. Data Processing and Final Products 5
1.4. Topographic Relief and cultural features 5
2. DATA ACQUISITION 6
2.1. Survey Area 6
2.2. Survey Operations 6
2.3. Flight Specifications 7
2.4. Aircraft and Equipment 8
2.4.1. Survey Aircraft 8
2.4.2. Electromagnetic System 8
2.4.3. Airborne magnetometer 10
2.4.4. Ancillary Systems 10
2.4.4.1. Radar Altimeter 10
2.4.4.2. GPS Navigation System 10
2.4.4.3. Digital Acquisition System 11
2.4.5. Base Station 11
3. PERSONNEL 12
4. DATA PROCESSING AND PRESENTATION 13
4.1. Flight Path 13
4.2. Electromagnetic Data 13
4.3. Magnetic Data 14
5. DELIVERABLES 15
5.1. Survey Report 15
5.2. Maps 15
5.3. Digital Data 15
6. CONCLUSIONS 19

APPENDICES

A. Survey block location map 20
B. Survey block coordinates 22
C. Modeling VTEM data 23
D. VTEM Waveform 24
E. Geophysical maps 25

REPORT ON A HELICOPTER-BORNE
VERSATILE TIME DOMAIN ELECTROMAGNETIC SURVEY

Rich property, Yukon, Canada

Executive Summary

This report describes the Helicopter-borne geophysical survey carried out on behalf of Southampton Ventures Inc. by Geotech Ltd. over one block in Yukon , Canada.

Principal geophysical sensors included a versatile time domain electromagnetic (VTEM) system and a cesium magnetometer. Ancillary equipment included a GPS navigation system and a radar altimeter. A total of 293.00 line-km were flown.

In-field data processing involved quality control and compilation of data collected during the acquisition stage, using the in-field processing centre established in Eagle Plains, Yukon. Preliminary and final data processing, including generation of final digital data products were done at the office of Geotech Ltd. in Aurora, Ontario.

The processed survey results are presented as electromagnetic stacked profiles and total magnetic intensity grid.

Digital data includes all electromagnetic and magnetic products plus positional, altitude and raw data.

1. INTRODUCTION

1.1 General Considerations

These services are the result of the Agreement made between Geotech Ltd. and Archer Cathro & Associates to perform a helicopter-borne geophysical survey over one block located in Yukon, Canada.

293.00 line-km of geophysical data were acquired during the survey.

Bill Wengzynowski, acted on behalf of Southampton Ventures Inc. during data acquisition and data processing phases of this project.

The survey block is as shown in Appendix A.

The crew was based in Eagle Plains, Yukon for the acquisition phase of the survey, as shown in Section 2 of this report.

The helicopter was based at the Eagle Plains airport for the duration of the survey. Survey flying was completed on August 27th, 2007. Preliminary data processing was carried out daily during the acquisition phase of the project. Final data presentation and data archiving was completed in the Aurora office of Geotech Ltd. in January, 2008.

1.2. Survey and System Specifications

The survey block was flown at nominal traverse line spacing of 300 metres, at N90°E / N270°E direction. Tie lines were flown perpendicular to traverse lines.

Where possible, the helicopter maintained a mean terrain clearance of 85 metres, which translated into an average height of 45 metres above ground for the bird-mounted VTEM system and 70 metres for the magnetic sensor.

The survey was flown using an Astar B3 helicopter, registration C-GTFX. The helicopter was operated by TRK helicopters. Details of the survey specifications may be found in Section 2 of this report.

1.3. Data Processing and Final Products

Data compilation and processing were carried out by the application of Geosoft OASIS Montaj and programs proprietary to Geotech Ltd.

A database, grids and maps of final products were presented to Southampton Ventures Inc.

The survey report describes the procedures for data acquisition, processing, final image presentation and the specifications for the digital data set.

1.4. Topographic Relief and cultural features

The survey block is located in Yukon, approximately 22 kilometers east of the town of Eagle Plains.

Topographically, the survey area exhibits a mountainous terrain, with elevation range from 480 metres to 960 metres above sea level.

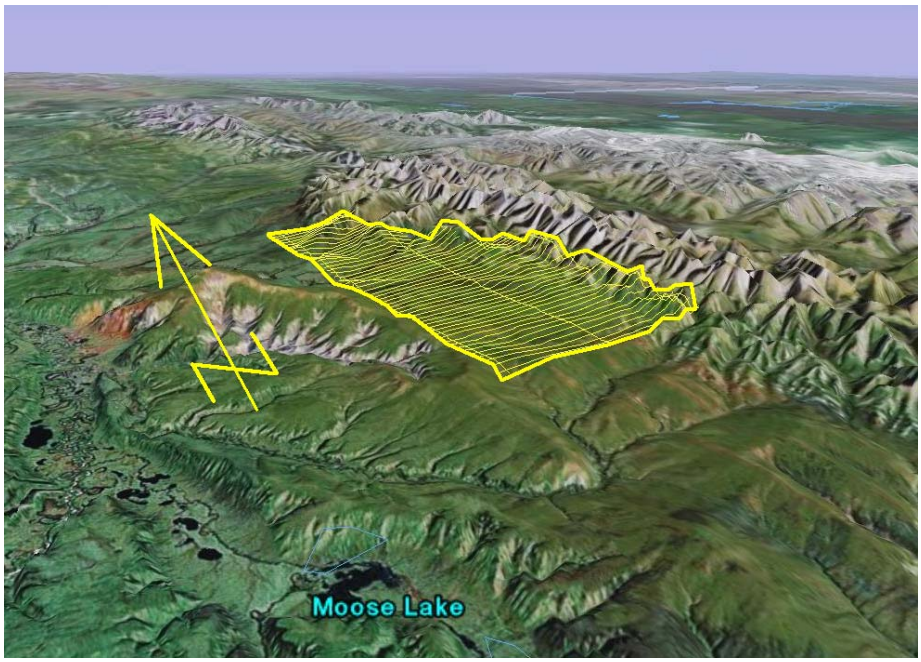

Figure 1. – Projection of flight path on topography.

2. DATA ACQUISITION

2.1. Survey Area

The survey block (see location map, Appendix A) and general flight specifications are as follows:

Survey block	Line spacing (m)	Area (Km2)	Line-km	Flight direction	Line number
RICH	300	74	257	N90E / N270E	L22010 - L22510
	3000		36	N0E / N180E	T22910 - T22930

Table 1 - Survey block

Survey block boundaries co-ordinates are provided in Appendix B.

2.2. Survey Operations

Survey operations were based in Eagle Plains, Yukon for the acquisition phase of the survey.
The following table shows the timing of the flying.

Date	Flight #	Flown KM	Block	Crew Location	Comments
26-Aug-07	68	122.00	RICH	Eagle Plains, Yukon	Mobilization, Production
27-Aug-07	69, 70	171.00	RICH	Eagle Plains, Yukon	Production – block complete

Table 2 - Survey schedule

2.3. Flight Specifications

The nominal EM sensor terrain clearance was 45 m (EM bird height above ground, i.e. helicopter is maintained 85 m above ground) due to rough terrain and helicopter crew safety. Nominal survey speed was 80 km/hour. The data recording rates of the data acquisition was 0.1 second for electromagnetics and magnetometer, 0.2 second for altimeter and GPS. This translates to a geophysical reading about every 2 metres along flight track. Navigation was assisted by a GPS receiver and data acquisition system, which reports GPS co-ordinates as latitude/longitude and directs the pilot over a pre-programmed survey grid.

The operator was responsible for monitoring of the system integrity. He also maintained a detailed flight log during the survey, tracking the times of the flight as well as any unusual geophysical or topographic feature.

On return of the aircrew to the base the survey data was transferred from a compact flash card (PCMCIA) to the data processing computer.

2.4. Aircraft and Equipment

2.4.1. Survey Aircraft

An Astar B3 helicopter, registration C-GTFX - owned and operated by TRK Helicopters Ltd. - was used for the survey. Installation of the geophysical and ancillary equipment was carried out by Geotech Ltd.

2.4.2. Electromagnetic System

The electromagnetic system was a Geotech Time Domain EM (VTEM) system. The configuration is as indicated in Figure 2 below.

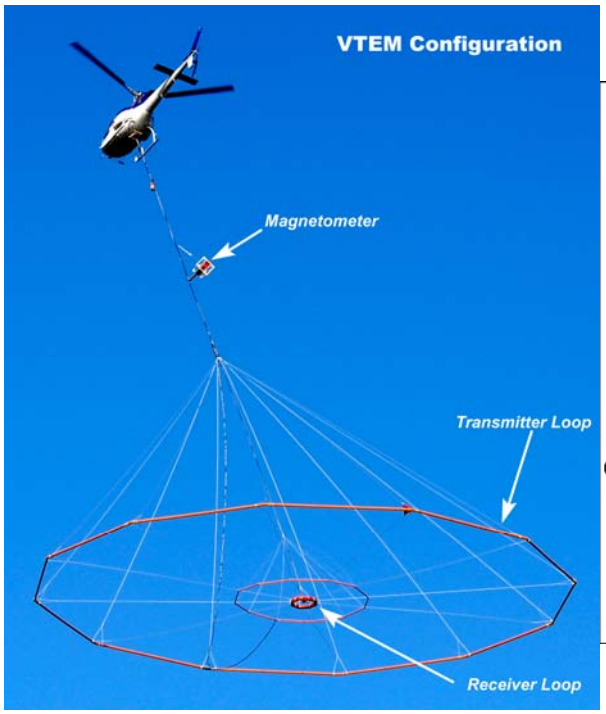

Figure 2 – VTEM configuration

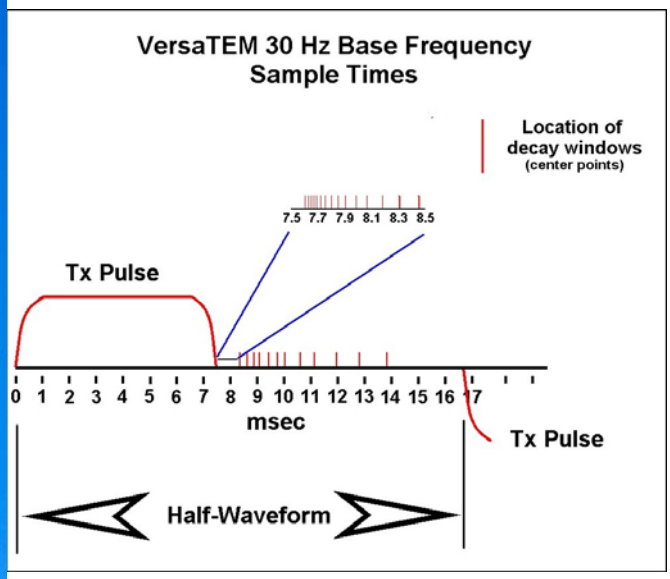

Figure 3 – Sample times

Receiver and transmitter coils are concentric and Z-direction oriented.
The receiver decay recording scheme is shown diagrammatically in Figure 3.

Twenty-four measurement gates were used in the range from 120 μs to 6578 μs, as shown in Table 3.

VTEM Decay Sampling scheme				
Array Index	(Microseconds)			
	Time Gate	Start	End	Width
10	120	110	131	21
11	141	131	154	24
12	167	154	183	29
13	198	183	216	34
14	234	216	258	42
15	281	258	310	53
16	339	310	373	63
17	406	373	445	73
18	484	445	529	84
19	573	529	628	99
20	682	628	750	123
21	818	750	896	146
22	974	896	1063	167
23	1151	1063	1261	198
24	1370	1261	1506	245
25	1641	1506	1797	292
26	1953	1797	2130	333
27	2307	2130	2526	396
28	2745	2526	3016	490
29	3286	3016	3599	583
30	3911	3599	4266	667
31	4620	4266	5058	792
32	5495	5058	6037	979
33	6578	6037	7203	1167

Table 3 - VTEM decay sampling scheme

Transmitter coil diameter was 26 metres, the number of turns was 4.
Transmitter pulse repetition rate was 30 Hz.
Peak current was 198 Amp.
Pulse width was 7.2 ms
Duty cycle was 43%.
Peak dipole moment was 420,500 NIA.

Receiver coil diameter was 1.2 metre, the number of turns was 100.
Receiver effective area was 113.1 m^2
Wave form – trapezoid.
Recording sampling rate was 10 samples per second.

The EM bird was towed 42 m below the helicopter.

2.4.3. Airborne magnetometer

The magnetic sensor utilized for the survey was a Geometrics optically pumped cesium vapour magnetic field sensor, mounted in a separated bird, towed 15 metres below the helicopter, as shown on figure 1. The sensitivity of the magnetic sensor is 0.02 nanoTesla (nT) at a sampling interval of 0.1 seconds. The magnetometer sends the measured magnetic field strength as nanoTeslas to the data acquisition system via the RS-232 port.

2.4.4. Ancillary Systems

2.4.4.1. Radar Altimeter

A Terra TRA 3000/TRI 40 radar altimeter was used to record terrain clearance. The antenna was mounted beneath the bubble of the helicopter cockpit.

2.4.4.2. GPS Navigation System

The navigation system used was a Geotech PC based navigation system utilizing a NovAtel's WAAS enable OEM4-G2-3151W GPS receiver, Geotech navigate software, a full screen display with controls in front of the pilot to direct the flight and an NovAtel GPS antenna mounted on the helicopter tail.
The co-ordinates of the block were set-up prior to the survey and the information was fed into the airborne navigation system.

2.4.4.3. Digital Acquisition System

A Geotech data acquisition system recorded the digital survey data on an internal compact flash card. Data is displayed on an LCD screen as traces to allow the operator to monitor the integrity of the system. The data type and sampling interval as provided in table 4.

DATA TYPE	SAMPLING
TDEM	0.1 sec
Magnetometer	0.1 sec
GPS Position	0.2 sec
RadarAltimeter	0.2 sec

Table 4 - Sampling Rates

2.4.5. Base Station

A combine magnetometer/GPS base station was utilized on this project. A Geometrics Cesium vapour magnetometer was used as a magnetic sensor with a sensitivity of 0.001 nT. The base station was recording the magnetic field together with the GPS time at 1 Hz on a base station computer.

The base station magnetometer sensor was installed 100 metres from the airport in Eagle Plains, away from electric transmission lines and moving ferrous objects such as motor vehicles.

The magnetometer base station's data was backed-up to the data processing computer at the end of each survey day.

3. PERSONNEL

The following Geotech Ltd. personnel were involved in the project:

Field

Project Manager:	Harish Kumar
Operator:	Keith Lavelley
Crew chief / QC Geophysicist:	Sean Hayes

The survey pilot and the mechanic engineer were employed directly by the helicopter operator – TRK Helicopters Ltd.

Pilot:	Roy Stevenson
Engineer:	Darren Shipman

Office

Data Processing / Reporting:	George Lev
Data Technician:	Maria Jagodkin

Data acquisition and processing phases were carried out under the supervision of Andrei Bagrianski, Surveys Manager. Overall management of the project was undertaken by Edward Morrison, President, Geotech Ltd.

4. DATA PROCESSING AND PRESENTATION

4.1. Flight Path

The flight path, recorded by the acquisition program as WGS 84 latitude/longitude, was converted into the UTM coordinate system in Oasis Montaj.

The flight path was drawn using linear interpolation between x, y positions from the navigation system. Positions are updated every second and expressed as UTM eastings (x) and UTM northings (y).

4.2. Electromagnetic Data

A three stage digital filtering process was used to reject major sferic events and to reduce system noise. Local sferic activity can produce sharp, large amplitude events that cannot be removed by conventional filtering procedures. Smoothing or stacking will reduce their amplitude but leave a broader residual response that can be confused with geological phenomena. To avoid this possibility, a computer algorithm searches out and rejects the major sferic events. The filter used was a 16 point non-linear filter.

The signal to noise ratio was further improved by the application of a low pass linear digital filter. This filter has zero phase shift which prevents any lag or peak displacement from occurring, and it suppresses only variations with a wavelength less than about 1 second or 20 metres. This filter is a symmetrical 1 sec linear filter.

The results are presented as stacked profiles of EM voltages for the time gates, in linear - logarithmic scale for both B-field and dB/dt response.

Generalized modeling results of the VTEM system, written by Geophysicist Roger Barlow, are shown in Appendix C.

Graphical representation of the VTEM output voltage of the receiver coil and the transmitter current is shown in Appendix D.

4.3. Magnetic Data

The processing of the magnetic data involved the correction for diurnal variations by using the digitally recorded ground base station magnetic values. The base station magnetometer data was edited and merged into the Geosoft GDB database on a daily basis. The aeromagnetic data was corrected for diurnal variations by subtracting the observed magnetic base station deviations.

A micro-levelling procedure was applied to remove persistent low-amplitude components of flight-line noise remaining in the data. Where Tie lines were available, Tie line levelling was carried out by adjusting intersection points along the traverse lines.

The corrected magnetic data was interpolated between survey lines using a random point gridding method to yield x-y grid values for a standard grid cell size of approximately 0.1 cm at the mapping scale. The Minimum Curvature algorithm was used to interpolate values onto a rectangular regular spaced grid.

The survey area shows an average magnetic activity. Maximum values of 58142 nT are observed in the NW part of the block. Average of 58083 nT is detected in the survey area.

5. DELIVERABLES

5.1. Survey Report

The survey report describes the data acquisition, processing, and final presentation of the survey results.

The survey report is provided in two paper copies and digitally in PDF format.

5.2. Maps

Final maps were produced at a scale of 1:25,000. The coordinate/projection system used was the WGS84, UTM zone 8N. All maps show the flight path trace and topographic data. Latitude and longitude are also noted on maps.

The following maps are presented on paper,

- dB/dt profiles, Time Gates 0.234 – 6.578 ms in linear - logarithmic scale
- B-field profiles, Time Gates 0.234 – 6.578 ms in linear - logarithmic scale
- Total Magnetic intensity contours and colour image

5.3. Digital Data

Two copies of DVDs were prepared.

There are two (2) main directories,

Data contains a database, grids and maps, as described below.

Report contains a copy of the report and appendices in PDF format.

a kml file containing flightpath of the RICH property.
A free version of Google Earth software can be downloaded from,
http://earth.google.com/download-earth.html

- Database in Geosoft GDB format, containing the following channels:

X:	X positional data (metres – WGS84, utm zone 8 north)
Y:	Y positional data (metres – WGS84, utm zone 8 north)
Z:	GPS antenna elevation (metres - ASL)
Radar:	Helicopter terrain clearance from radar altimeter (metres - AGL)
Radarb:	EM Loop terrain clearance from radar altimeter (metres - AGL)
DEM:	Digital elevation model (metres)
Gtime1:	GPS time (seconds of the day)
Mag1:	Raw Total Magnetic field data (nT)
Basemag:	Magnetic diurnal variation data (nT)
Mag2:	Total Magnetic field diurnal variation corrected data (nT)
Mag3:	Leveled Total Magnetic field data (nT)
SF[10]:	dB/dt 120 microsecond time channel (pV/A/m^4)
SF[11]:	dB/dt 141 microsecond time channel (pV/A/m^4)
SF[12]:	dB/dt 167 microsecond time channel (pV/A/m^4)
SF[13]:	dB/dt 198 microsecond time channel (pV/A/m^4)
SF[14]:	dB/dt 234 microsecond time channel (pV/A/m^4)
SF[15]:	dB/dt 281 microsecond time channel (pV/A/m^4)
SF[16]:	dB/dt 339 microsecond time channel (pV/A/m^4)
SF[17]:	dB/dt 406 microsecond time channel (pV/A/m^4)
SF[18]:	dB/dt 484 microsecond time channel (pV/A/m^4)
SF[19]:	dB/dt 573 microsecond time channel (pV/A/m^4)
SF[20]:	dB/dt 682 microsecond time channel (pV/A/m^4)
SF[21]:	dB/dt 818 microsecond time channel (pV/A/m^4)
SF[22]:	dB/dt 974 microsecond time channel (pV/A/m^4)
SF[23]:	dB/dt 1151 microsecond time channel (pV/A/m^4)
SF[24]:	dB/dt 1370 microsecond time channel (pV/A/m^4)
SF[25]:	dB/dt 1641 microsecond time channel (pV/A/m^4)
SF[26]:	dB/dt 1953 microsecond time channel (pV/A/m^4)
SF[27]:	dB/dt 2307 microsecond time channel (pV/A/m^4)
SF[28]:	dB/dt 2745 microsecond time channel (pV/A/m^4)
SF[29]:	dB/dt 3286 microsecond time channel (pV/A/m^4)
SF[30]:	dB/dt 3911 microsecond time channel (pV/A/m^4)
SF[31]:	dB/dt 4620 microsecond time channel (pV/A/m^4)
SF[32]:	dB/dt 5495 microsecond time channel (pV/A/m^4)
SF[33]:	dB/dt 6578 microsecond time channel (pV/A/m^4)
BF[10]:	B-field 120 microsecond time channel (pV*ms)/(A*m^4)
BF[11]:	B-field 141 microsecond time channel (pV*ms)/(A*m^4)
BF[12]:	B-field 167 microsecond time channel (pV*ms)/(A*m^4)
BF[13]:	B-field 198 microsecond time channel (pV*ms)/(A*m^4)
BF[14]:	B-field 234 microsecond time channel (pV*ms)/(A*m^4)

BF[15]: B-field 281 microsecond time channel (pV*ms)/(A*m^4)
BF[16]: B-field 339 microsecond time channel (pV*ms)/(A*m^4)
BF[17]: B-field 406 microsecond time channel (pV*ms)/(A*m^4)
BF[18]: B-field 484 microsecond time channel (pV*ms)/(A*m^4)
BF[19]: B-field 573 microsecond time channel (pV*ms)/(A*m^4)
BF[20]: B-field 682 microsecond time channel (pV*ms)/(A*m^4)
BF[21]: B-field 818 microsecond time channel (pV*ms)/(A*m^4)
BF[22]: B-field 974 microsecond time channel (pV*ms)/(A*m^4)
BF[23]: B-field 1151 microsecond time channel (pV*ms)/(A*m^4)
BF[24]: B-field 1370 microsecond time channel (pV*ms)/(A*m^4)
BF[25]: B-field 1641 microsecond time channel (pV*ms)/(A*m^4)
BF[26]: B-field 1953 microsecond time channel (pV*ms)/(A*m^4)
BF[27]: B-field 2307 microsecond time channel (pV*ms)/(A*m^4)
BF[28]: B-field 2745 microsecond time channel (pV*ms)/(A*m^4)
BF[29]: B-field 3286 microsecond time channel (pV*ms)/(A*m^4)
BF[30]: B-field 3911 microsecond time channel (pV*ms)/(A*m^4)
BF[31]: B-field 4620 microsecond time channel (pV*ms)/(A*m^4)
BF[32]: B-field 5495 microsecond time channel (pV*ms)/(A*m^4)
BF[33]: B-field 6578 microsecond time channel (pV*ms)/(A*m^4)
PLM: Power line monitor

Electromagnetic B-field and dB/dt data is found in array channel format between indexes 10 – 33, as described above.

- Database 7067rich_wform.gdb in Geosoft GDB format, containing the following channels:

  Time: Sampling rate interval, 10.416 microseconds
  Volt: output voltage of the receiver coil (volt)

- Grids in Geosoft GRD format, as follow,

  Rich_magfin: Total magnetic intensity (nT)
  Rich_DEM: Digital elevation model (m)

  A Geosoft .GRD file has a .GI metadata file associated with it, containing grid projection information.
  Grid cell size of 10 metres was used.

- Maps at 1:25,000 scale in Geosoft MAP format, as follow,

  Rich_Magfin: Total magnetic intensity contours and colour image
  Rich_dBdt: VTEM dB/dt profiles, Time Gates 0.234 – 6.578 ms in linear - logarithmic scale
  Rich_EMLP: VTEM B-field profiles, Time Gates 0.234 – 6.578 ms in linear - logarithmic scale

- A *readme.txt* file describing the content of digital data, as described above.

6. CONCLUSIONS

A helicopter-borne versatile time domain electromagnetic (VTEM) geophysical survey has been completed over the Rich property, located in Yukon, Canada.

The total area coverage is 74.00 km^2. Total survey line coverage is 293.00 line kilometres. The principal sensors included a Time Domain EM system and a magnetometer. Results have been presented as stacked profiles and contour colour images at a scale of 1:25,000.

Final data processing at the office of Geotech Ltd. in Aurora, Ontario was carried out under the supervision of Andrei Bagrianski, Surveys Manager.

A number of EM anomaly groupings were identified. Ground follow-up of those anomalies should be carried out if favourably supported by other geoscientific data.

Respectfully submitted,

George Lev
Geotech Ltd.
January, 2008

APPENDIX A

SURVEY BLOCK LOCATION MAP

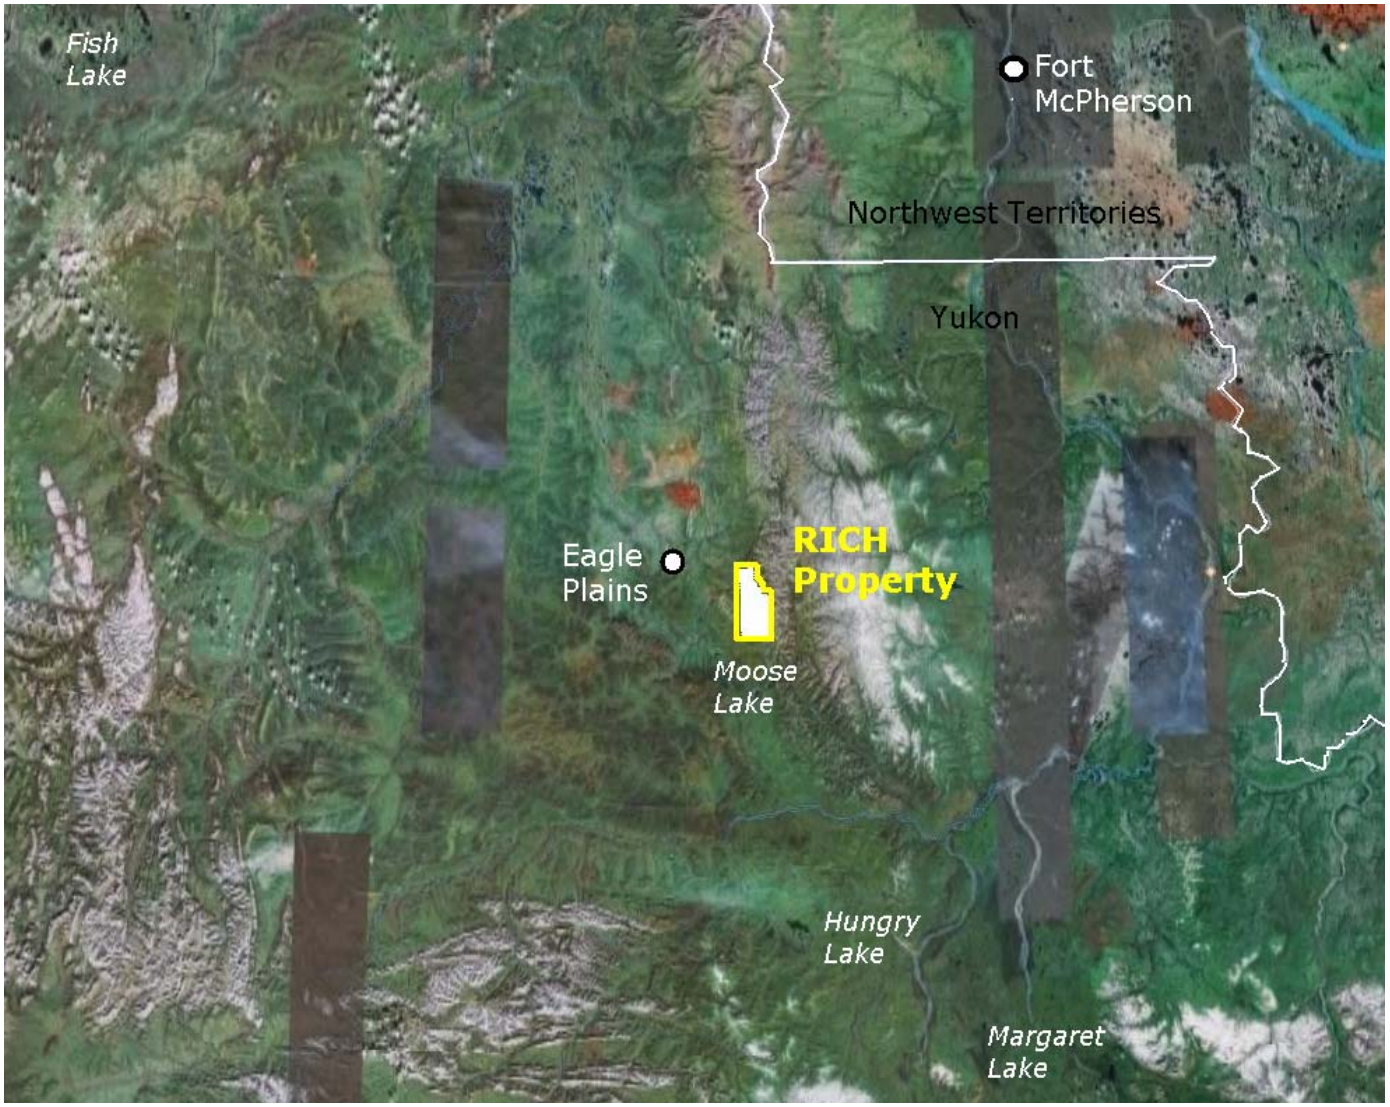

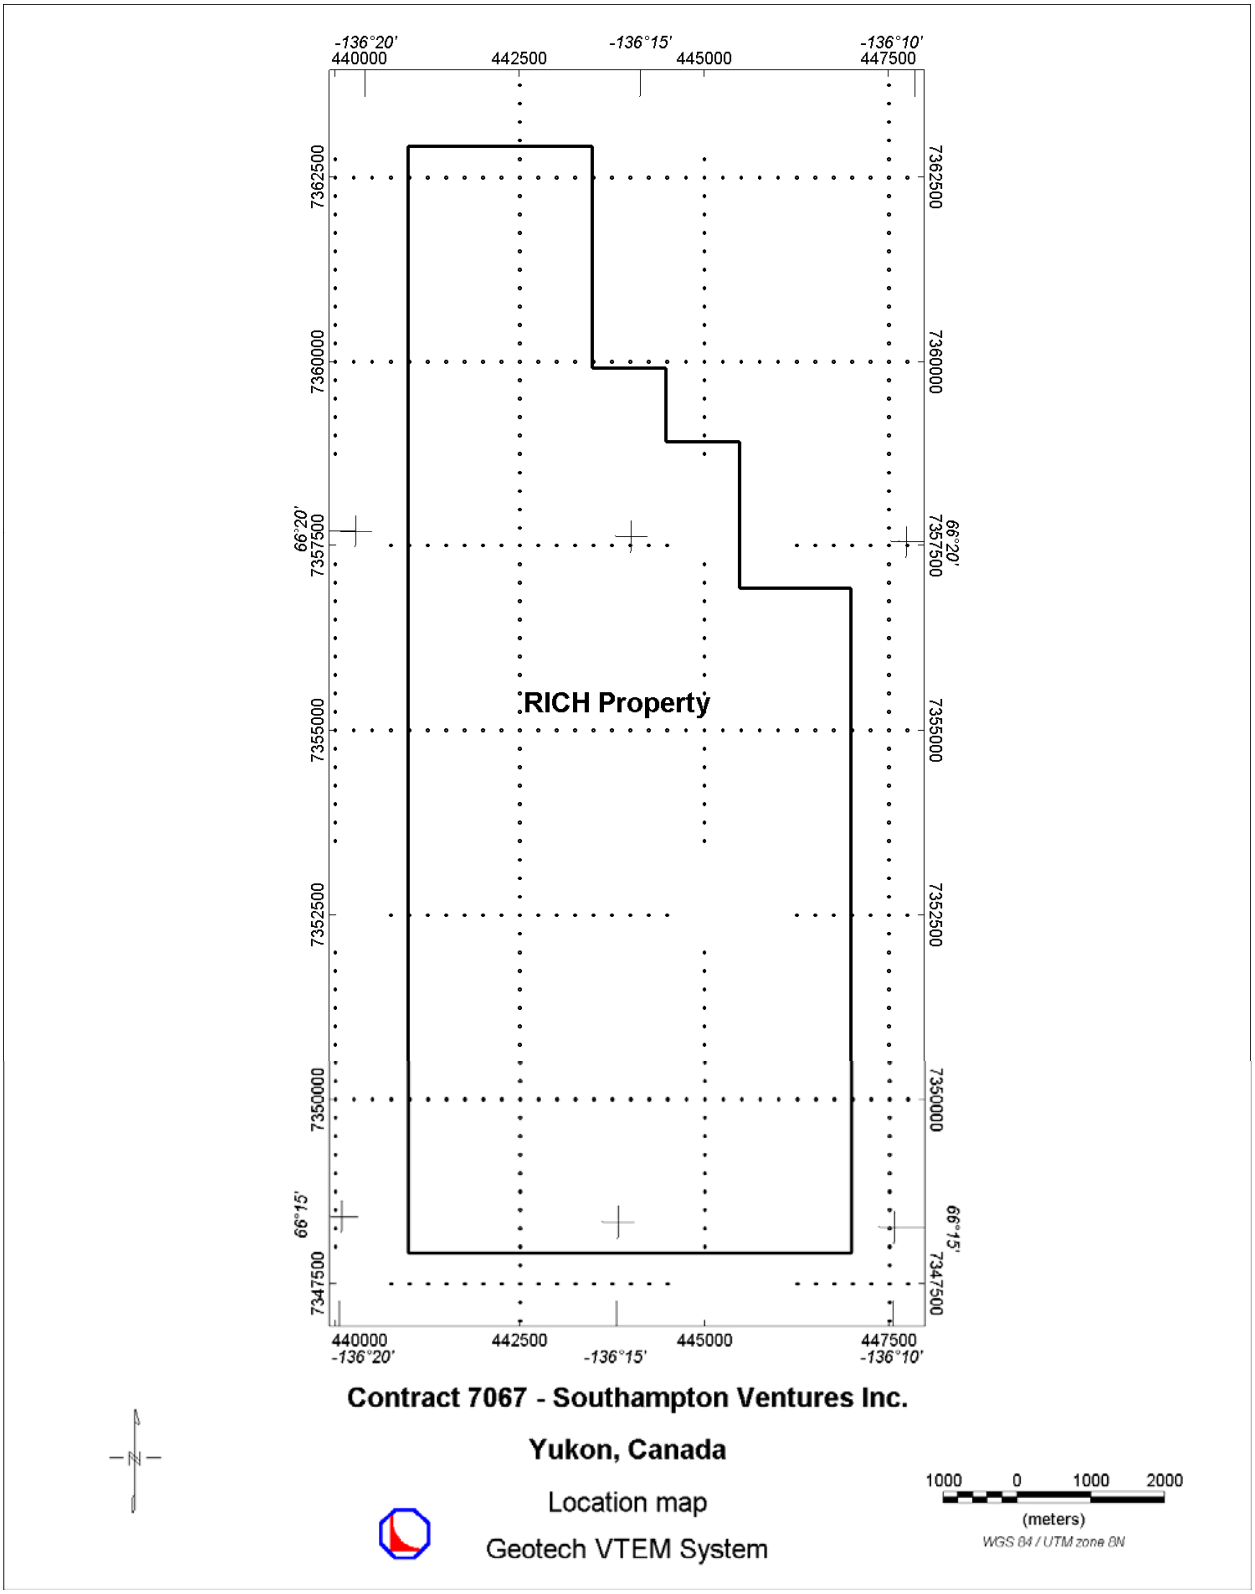
-136°20'
440000
442500
-136°15'
445000
447500
-136°10'
7362500
7360000
66°20'
7357500
7355000
7352500
7350000
66°15'
7347500
RICH Property
Contract 7067 - Southampton Ventures Inc.
Yukon, Canada
Location map
Geotech VTEM System
1000 0 1000 2000
(meters)
WGS 84 / UTM zone 8N

APPENDIX B

SURVEY BLOCK COORDINATES
(WGS 84, UTM zone 8 north)

Rich property

RICH	
Easting	**Northing**
440981	7362919
443481	7362919
443481	7359919
444481	7359919
444481	7358919
445481	7358919
445481	7356919
446981	7356919
446981	7347919
440981	7347919
440981	7362919

APPENDIX C

MODELING VTEM DATA

APPENDIX D

VTEM WAVEFORM

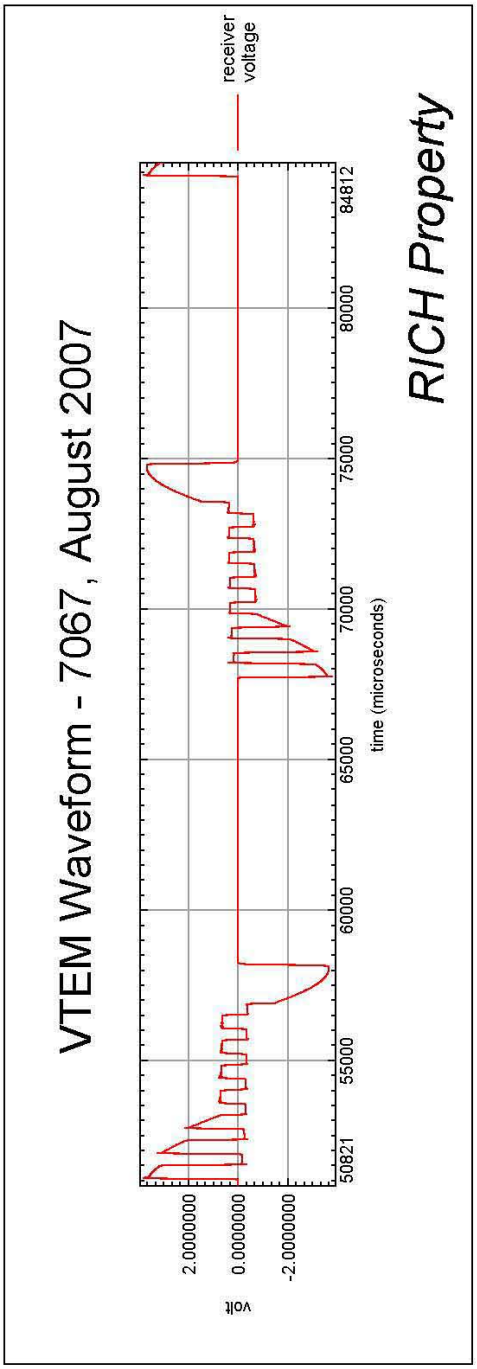

APPENDIX E

GEOPHYSICAL MAP

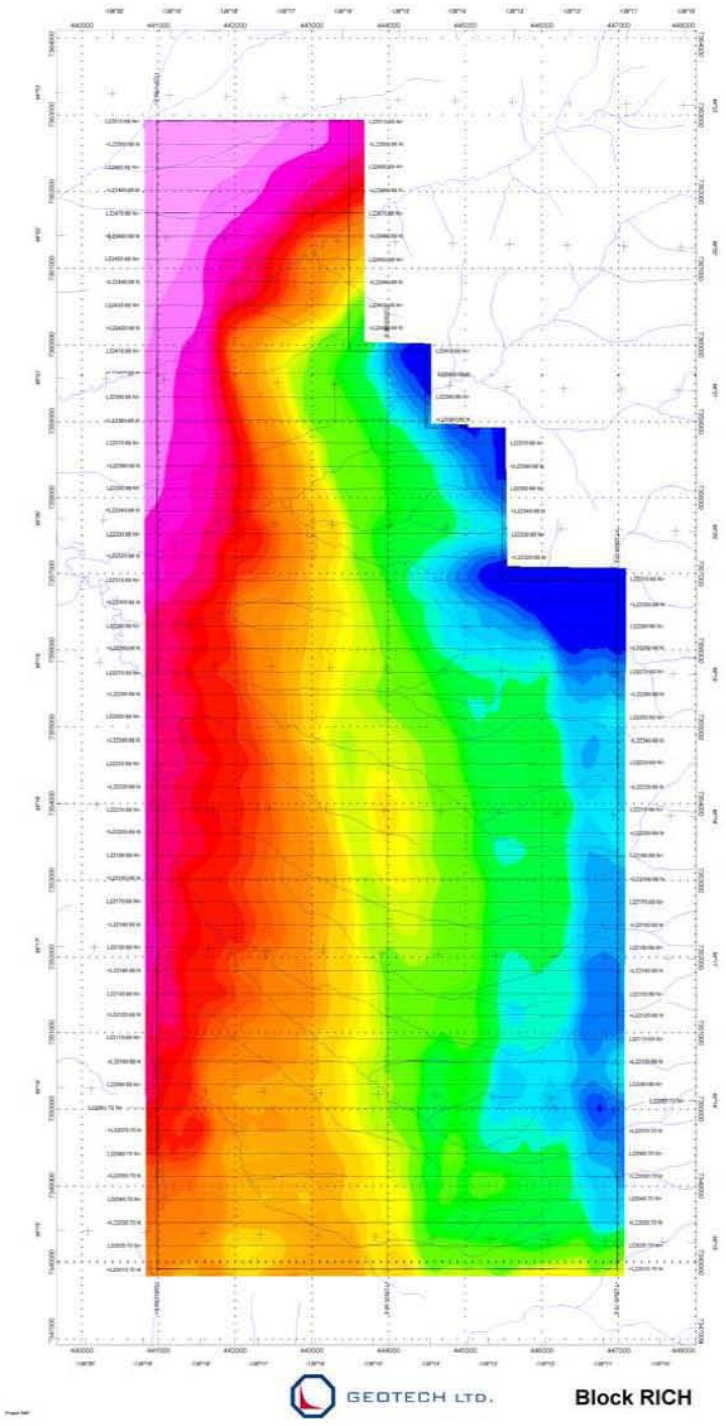

MODELING VTEM DATA

Introduction

The VTEM system is based on a concentric or central loop design, whereby, the receiver is positioned at the centre of a 26.1 meters diameter transmitter loop that produces a dipole moment up to 625,000 NIA at peak current. The wave form is a bi-polar, modified square wave with a turn-on and turn-off at each end. With a base frequency of 30 Hz, the duration of each pulse is approximately 7.5 milliseconds followed by an off time where no primary field is present.

During turn-on and turn-off, a time varying field is produced (dB/dt) and an electro-motive force (emf) is created as a finite impulse response. A current ring around the transmitter loop moves outward and downward as time progresses. When conductive rocks and mineralization are encountered, a secondary field is created by mutual induction and measured by the receiver at the centre of the transmitter loop.

Measurements are made during the off-time, when only the secondary field (representing the conductive targets encountered in the ground) is present.

Late in 2006, Geotech Ltd. incorporated a B-Field measurement in the VTEM system. The B-Field measurements have the advantage of containing more spectral energy at low spectral frequencies than the dB/dt measurements; hence, greater amplitudes and accuracies when encountering targets with higher conductances (> 500 Siemens). The converse is true at higher spectral frequencies where dB/dt measurements are best applied. The B-field is most widely used in nickel exploration where a small percentage of targets are extremely conductive (> 2500 Siemens) and less resolvable or invisible (below the noise threshold) using dB/dt measurements.

Efficient modeling of the results can be carried out on regularly shaped geometries, thus yielding close approximations to the parameters of the measured targets. The following is a description of a series of common models made for the purpose of promoting a general understanding of the measured results.

Variation of Plate Depth

Geometries represented by plates of different strike length, depth extent, dip, plunge and depth below surface can be varied with characteristic parameters like conductance of the target, conductance of the host and conductivity/thickness and thickness of the overburden layer.

Diagrammatic models for a vertical plate are shown in figures A and G at two different depths, all other parameters remaining constant. With this transmitter-receiver geometry, the classic **M** shaped response is generated. Figure A shows a plate where the top is near surface. Here, amplitudes of the duel peaks are higher and symmetrical with the zero centre positioned directly above the plate. Most important is the separation distance of the peaks. This distance is small when the plate is near surface and widens with a linear relationship as the plate (depth to top) increases. Figure G shows a much deeper plate where the separation distance of the peaks is much wider and the amplitudes of the channels have decreased.

Variation of Plate Dip

As the plate dips and departs from the vertical position, the peaks become asymmetrical. Figure B shows a near surface plate dipping 80º. Note that the direction of dip is toward the high shoulder of the response and the top of the plate remains under the centre minimum.

As the dip increases, the aspect ratio (Min/Max) decreases and this aspect ratio can be used as an empirical guide to dip angles from near 90º to about 30º. The method is not sensitive enough where dips are less than about 30º. Figure E shows a plate dipping 45º and, at this angle, the minimum shoulder starts to vanish. In Figure D, a flat lying plate is shown, relatively near surface. Note that the twin peak anomaly has been replaced by a symmetrical shape with large, bell shaped, channel amplitudes which decay relative to the conductance of the plate.

Figure H shows a special case where two plates are positioned to represent a synclinal structure. Note that the main characteristic to remember is the centre amplitudes are higher (approximately double) compared to the high shoulder of a single plate. This model is very representative of tightly folded formations where the conductors where once flat lying.

Variation of Prism Depth

Finally, with prism models, another algorithm is required to represent current on the plate. A plate model is considered to be infinitely thin with respect to thickness and incapable of representing the current in the thickness dimension. A prism model is constructed to deal with this problem, thereby, representing the thickness of the body more accurately.

Figures C, F and I show the same prism at increasing depths. Aside from an expected decrease in amplitude, the side lobes of the anomaly show a widening with deeper prism depths of the bell shaped early time channels.

A

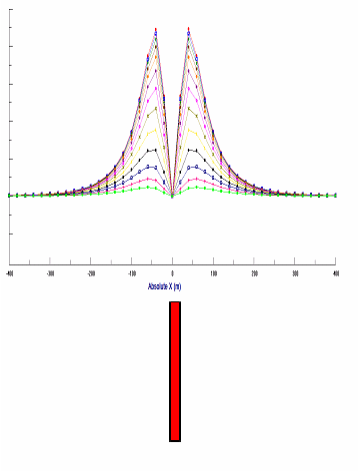

B

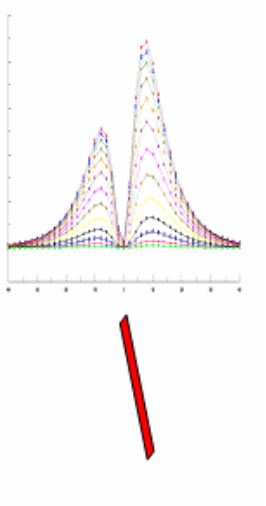

C

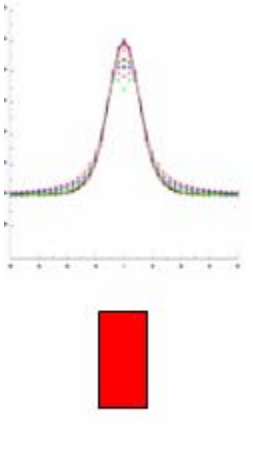

D

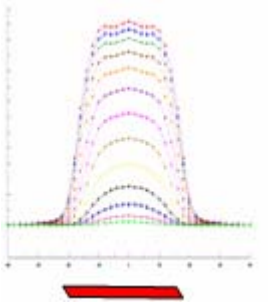

E

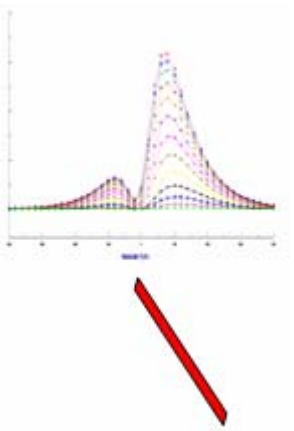

F

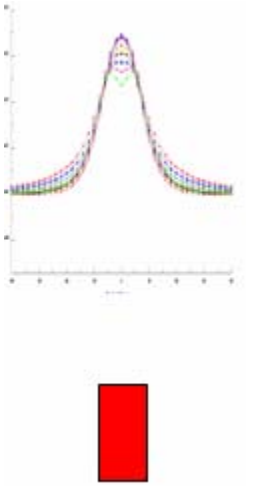

G

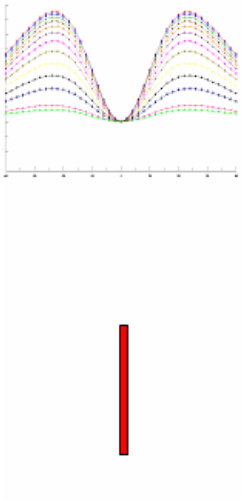

H

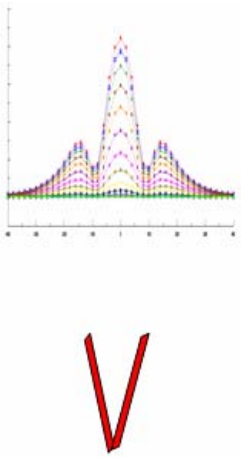

I

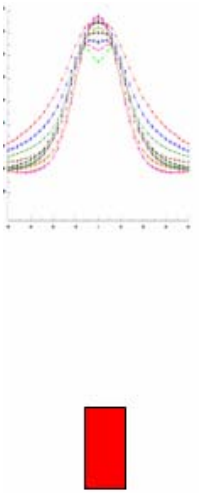

General Modeling Concepts

A set of models has been produced for the Geotech VTEM® system with explanation notes (see models A to I above). The reader is encouraged to review these models, so as to get a general understanding of the responses as they apply to survey results. While these models do not begin to cover all possibilities, they give a general perspective on the simple and most commonly encountered anomalies.

When producing these models, a few key points were observed and are worth noting as follows:

- For near vertical and vertical plate models, the top of the conductor is always located directly under the centre low point between the two shoulders in the classic **M** shaped response.

- As the plate is positioned at an increasing depth to the top, the shoulders of the **M** shaped response, have a greater separation distance.

- When faced with choosing between a flat lying plate and a prism model to represent the target (broad response) some ambiguity is present and caution should be exercised.

- With the concentric loop system and Z-component receiver coil, virtually all types of conductors and most geometries are most always well coupled and a response is generated (see model H). Only concentric loop systems can map this type of target.

The modelling program used to generate the responses was prepared by PetRos Eikon Inc. and is one of a very few that can model a wide range of targets in a conductive half space.

General Interpretation Principals

Magnetics

The total magnetic intensity responses reflect major changes in the magnetite and/or other magnetic minerals content in the underlying rocks and unconsolidated overburden. Precambrian rocks have often been subjected to intense heat and pressure during structural and metamorphic events in their history. Original signatures imprinted on these rocks at the time of formation have, it most cases, been modified, resulting in low magnetic susceptibility values.

The amplitude of magnetic anomalies, relative to the regional background, helps to assist in identifying specific magnetic and non-magnetic rock units (and conductors) related to, for example, mafic flows, mafic to ultramafic intrusives, felsic intrusives, felsic volcanics and/or sediments etc. Obviously, several geological sources can produce the same magnetic response. These ambiguities can be reduced considerably if basic geological information on the area is available to the geophysical interpreter.

In addition to simple amplitude variations, the shape of the response expressed in the wave length and the symmetry or asymmetry, is used to estimate the depth, geometric parameters and magnetization of the anomaly. For example, long narrow magnetic linears usually reflect mafic flows or intrusive dyke features. Large areas with complex magnetic patterns may be produced by intrusive bodies with significant magnetization, flat lying magnetic sills or sedimentary iron formation. Local isolated circular magnetic patterns often represent plug-like igneous intrusives such as kimberlites, pegmatites or volcanic vent areas.

Because the total magnetic intensity (TMI) responses may represent two or more closely spaced bodies within a response, the second derivative of the TMI response may be helpful for distinguishing these complexities. The second derivative is most useful in mapping near surface linears and other subtle magnetic structures that are partially masked by nearby higher amplitude magnetic features. The broad zones of higher magnetic amplitude, however, are severely attenuated in the vertical derivative results. These higher amplitude zones reflect rock units having strong magnetic susceptibility signatures. For this reason, both the TMI and the second derivative maps should be evaluated together.

Theoretically, the second derivative, zero contour or colour delineates the contacts or limits of large sources with near vertical dip and shallow depth to the top. The vertical gradient map also aids in determining contact zones between rocks with a susceptibility contrast, however, different, more complicated rules of thumb apply.

Concentric Loop EM Systems

Concentric systems with horizontal transmitter and receiver antennae produce much larger responses for flat lying conductors as contrasted with vertical plate-like conductors. The amount of current developing on the flat upper surface of targets having a substantial area in this dimension, are the direct result of the effective coupling angle, between the primary magnetic field and the flat surface area. One therefore, must not compare the amplitude/conductance of responses generated from flat lying bodies with those derived from near vertical plates; their ratios will be quite different for similar conductances.

Determining dip angle is very accurate for plates with dip angles greater than 30º. For angles less than 30º to 0º, the sensitivity is low and dips can not be distinguished accurately in the presence of normal survey noise levels.

A plate like body that has near vertical position will display a two shoulder, classic **M** shaped response with a distinctive separation distance between peaks for a given depth to top.

It is sometimes difficult to distinguish between responses associated with the edge effects of flat lying conductors and poorly conductive bedrock conductors. Poorly conductive bedrock conductors having low dip angles will also exhibit responses that may be interpreted as surfacial overburden conductors. In some situations, the conductive response has line to line continuity and some magnetic correlation providing possible evidence that the response is related to an actual bedrock source.

The EM interpretation process used, places considerable emphasis on determining an understanding of the general conductive patterns in the area of interest. Each area has different characteristics and these can effectively guide the detailed process used.

The first stage is to determine which time gates are most descriptive of the overall conductance patterns. Maps of the time gates that represent the range of responses can be very informative.

Next, stacking the relevant channels as profiles on the flight path together with the second vertical derivative of the TMI is very helpful in revealing correlations between the EM and Magnetics.

Next, key lines can be profiled as single lines to emphasize specific characteristics of a conductor or the relationship of one conductor to another on the same line. Resistivity Depth sections can be constructed to show the relationship of conductive overburden or conductive bedrock with the conductive anomaly.

GEOTECH LTD.

Survey Specifications:
Dates Flown: August 26-27, 2007
Survey Base: Eagle Plains, YT
Aircraft: Astar B3 helicopter, Registration C-GTFX
Nominal Flight Line Spacing: 300 metres
Nominal Flight Line Directions: N90°E/N270°E
Nominal Tie Line Spacing: 3000 metres
Nominal Tie Line Directions: N0°E/N180°E
Nominal helicopter terrain clearance 85 metres
EM Loop is towed 42 metres under helicopter
Magnetic sensor is 15 metres under helicopter

Instruments:
Geotech Time Domain Electromagnetic System (VTEM) with concentric Rx/Tx geometry
Transmitter Loop Diameter 26 m, Base Frequency 30 Hz
Dipole Moment 420,500 NIA
Transmitter Wave Form: Trapezoid, Pulse Width 7.22 ms
Geometrics Optically-pumped,
High Sensitivity Cesium Magnetometer
Magnetometer Resolution 0.02 nT at 10 samples/sec

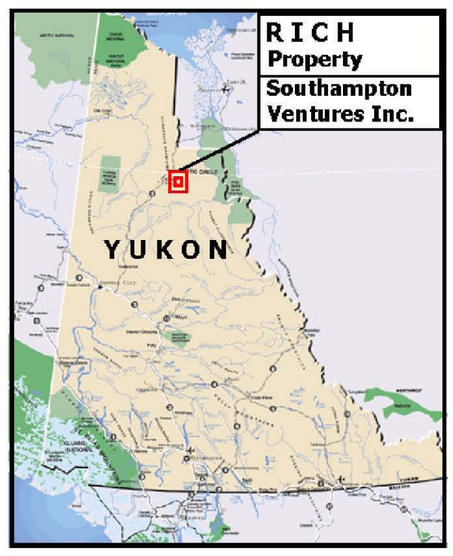

Magnetic field
(nT)

58112
58105
58101
58099
58097
58096
58095
58093
58092
58091
58090
58089
58087
58086
58085
58084
58082
58081
58080
58079
58078
58076
58075
58074
58073
58072
58071
58070
58069
58068
58067
58066
58065
58064

Contour intervals:

Legend:
Boundary Yukon - BC
Roads
Lakes, Rivers
Swamps
Topographic contours

Scale 1:25000
250 0 250 500 750 1000 1250
(meters)
WGS 84 / UTM zone 8N

Southampton Ventures Inc.
Block RICH
Yukon, Canada

Geotech VTEM System
Total Magnetic Field Map

Flown and processed by Geotech Ltd.
Flown and processed by Geotech Ltd.
245 Industrial Parkway North,
Aurora, Ontario, Canada L4G 4C4
www.geotech.ca

January 2008

Project 7067

GEOTECH LTD.

Survey Specifications:

Dates Flown: August 26-27, 2007
Survey Base: Eagle Plains, YT
Aircraft: Astar B3 helicopter, Registration C-GTFX
Nominal Flight Line Spacing: 300 metres
Nominal Flight Line Directions: N90°E/N270°E
Nominal Tie Line Spacing: 3000 metres
Nominal Tie Line Directions: N0°E/N180°E
Nominal helicopter terrain clearance 85 metres
EM Loop is towed 42 metres under helicopter
Magnetic sensor is 15 metres under helicopter

Instruments:

Geotech Time Domain Electromagnetic System (VTEM)
with concentric Rx/Tx geometry
Transmitter Loop Diameter 26 m, Base Frequency 30 Hz
Dipole Moment 420,500 NIA
Transmitter Wave Form: Trapezoid, Pulse Width 7.22 ms
Geometrics Optically-pumped,
High Sensitivity Cesium Magnetometer
Magnetometer Resolution 0.02 nT at 10 samples/sec

Profiles scale 1 mm = 0.05 pV/A/m^4
(Linear between +/-0.2 pV/A/m^4
logarithmic above 0.2 pV/A/m^4)

0.234 ms
0.281 ms
0.339 ms
0.406 ms
0.484 ms
0.573 ms
0.682 ms
0.818 ms
0.974 ms
1.151 ms
1.370 ms
1.641 ms
1.953 ms
2.307 ms
2.745 ms
3.286 ms
3.911 ms
4.620 ms
5.495 ms
6.578 ms
7.828 ms

Legend:

Roads
Lakes, Rivers
Swamps
Topographic contours

Scale 1:25000

250 0 250 500 750 1000 1250
(meters)
WGS 84 / UTM zone 8N

Southampton Ventures Inc.
Block RICH
Yukon, Canada

Geotech VTEM System
dB/dt Profiles
Time Gates 0.234 - 6.578 ms

Flown and processed by Geotech Ltd.
245 Industrial Parkway North,
Aurora, Ontario, Canada L4G 4C4
www.geotech.ca

January 2008

Project 7067

GEOTECH LTD.

Survey Specifications:
- Dates Flown: August 26-27, 2007
- Survey Base: Eagle Plains, YT
- Aircraft: Astar B3 helicopter, Registration C-GTFX
- Nominal Flight Line Spacing: 300 metres
- Nominal Flight Line Directions: N90°E/N270°E
- Nominal Tie Line Spacing: 3000 metres
- Nominal Tie Line Directions: N0°E/N180°E
- Nominal helicopter terrain clearance 85 metres
- EM Loop is towed 42 metres under helicopter
- Magnetic sensor is 15 metres under helicopter

Instruments:
- Geotech Time Domain Electromagnetic System (VTEM) with concentric Rx/Tx geometry
- Transmitter Loop Diameter 26 m, Base Frequency 30 Hz
- Dipole Moment 420,500 NIA
- Transmitter Wave Form: Trapezoid, Pulse Width 7.22 ms
- Geometrics Optically-pumped,
- High Sensitivity Cesium Magnetometer
- Magnetometer Resolution 0.02 nT at 10 samples/sec

Profiles scale 1 mm = 0.05 (pV*ms)/A/m^4
(Linear between +/-0.2 (pV*ms)/A/m^4
logarithmic above 0.2 (pV*ms)/A/m^4)

- 0.234 ms (B-field)
- 0.281 ms (B-field)
- 0.339 ms (B-field)
- 0.406 ms (B-field)
- 0.484 ms (B-field)
- 0.573 ms (B-field)
- 0.682 ms (B-field)
- 0.818 ms (B-field)
- 0.974 ms (B-field)
- 1.151 ms (B-field)
- 1.370 ms (B-field)
- 1.641 ms (B-field)
- 1.953 ms (B-field)
- 2.307 ms (B-field)
- 2.745 ms (B-field)
- 3.286 ms (B-field)
- 3.911 ms (B-field)
- 4.620 ms (B-field)
- 5.495 ms (B-field)
- 6.578 ms (B-field)
- 7.828 ms (B-field)

Legend:
- Roads
- Lakes, Rivers
- Swamps
- Topographic contours

Scale 1:25000

250 0 250 500 750 1000 1250

(meters)

WGS 84 / UTM zone 8N

Southampton Ventures Inc.
Block RICH
Yukon, Canada

Geotech VTEM System

B-Field Profiles
Time Gates 0.234 - 6.578 ms

Flown and processed by Geotech Ltd.
245 Industrial Parkway North.,
Aurora, Ontario, Canada L4G 4C4
www.geotech.ca

January 2008

Project 7067

APPENDIX V

GEOLOGICAL AND GEOTECHNICAL LOGS

NiMo PROJECT

PROPERTY: Rich

HOLE: RI07-01

Easting	Northing	Elev.	Depth (m)
445464	7353241	679	60.96

Contractor: North Star
Drill: MD-001

SURVEY							
Depth (m)	Azimuth	Dip	Method	Depth (m)	Azimuth	Dip	Method
collar	090°	-55°	compass				

Core size: BTW
Casing depth: 14.33 (m) out

Drilling dates: July 14 to 17, 2007

Logged by: D. MacDonald

Target: _____

SUMMARY				
From (m)	To (m)	Interval	Unit	Comments
0.00	9.55	9.55	OVB	
9.55	60.96	51.41	DME	

SAMPLES
Numbers:
Total:
Date sent:

COMMENTS
Very bad ground conditions, hole abandonded.

PROPERTY: RICH **HOLE:** RI07-01

LITHOLOGY										ALT.			MINERALS				SAMPLES							Blocks			GEOTECHNICAL						JOINTS					
Struct.										ALT																		REC		RQD								
Type	Attitude	From (m)	To (m)	Interval (m)	Type	Unit	Texture	Modifier	Notes:				Ca	Sx	Fe		From (m)	To (m)	Interval (m)	Sample				From (m)	To (m)	Intvl. (m)	(m)	Percent	(m)	Percent	Weathering	Hardness	Frequency	Attitude	Shape	Roughness	Infilling
		0.00	9.55	9.55	OVB				Overburden	ex																										
		9.55	36.00	26.45	SHL	DME			9.55 - 36.00 m Black, cg, poorly lithified muddy sand, very friable (sand, not sandstone). No discernible structure, v	ex																												
BD	85	36.00	60.96	24.96	SHL	DME	LA	BK	36.00 - 36.50 m Highly fissile + extremely friable black, vfg organic-rich shale with rare limonite coating on some (5%) fracture surfaces. V poorly lithified, crumbles to touch.	ex					+										36.11	36.58	0.47	0.47	100	0.00	0	MW	VW	30	90	2	2	GYP
BD	80				SHL	DME	Fx	BK	36.50 - 45.72 m Finely laminar, v highly fissile and highly fractured BK SHL; too fragmented to see much structure	s														36.58	39.62	3.04	0.74	24	0.00	0	MW	MS	30	M	2	2	GYP
																								39.62	42.67	3.05	0.17	6	0.00	0	MW	VW	30	M	2	3	GYP
																								42.67	45.72	3.05	0.53	17	0.00	0	MW	VW	30	M	3	2	GYP
BD	80				SHL	DME	Fx	BK	45.72 - 57.91 m Extremely weathered BK SHL (sand) with unknown white, vfg alteration product at start of interval.	ex														45.72	48.77	3.05	0.62	20	0.00	0	HW	VW	30	M	5	4	GYP
																								48.77	51.82	3.05	0.70	23	0.00	0	HW	VW	30	M	3	3	GYP

PROPERTY: RICH **HOLE:** RI07-01

Struct.		LITHOLOGY								ALT.			MINERALS				SAMPLES							Blocks			GEOTECHNICAL						JOINTS				
										ALT																	REC		RQD									
Type	Attitude	From (m)	To (m)	Interval (m)	Type	Unit	Texture	Modifier	Notes:				Ca	Sx	Fe		From (m)	To (m)	Interval (m)	Sample				From (m)	To (m)	Intvl. (m)	(m)	Percent	(m)	Percent	Weathering	Hardness	Frequency	Attitude	Shape	Roughness	Infilling
																								51.82	54.87	3.05	0.74	24	0.00	0	HW	VW	30	M	3	3	GYP
																								54.87	57.91	3.04	1.02	34	0.00	0	HW	VW	30	M	3	3	GYP
BD	80				SHL	DME	Fx	BK	57.91 - 60.96 m EOH Highly fractured, finely laminar, BK SHL with unknown white, powdery alteration product through whole interval (doesn't fizz with HCl)	m-s														57.91	60.96	3.05	0.55	18	0.00	0	MW	MS	20	M	3	3	GYP
		60.96							END OF HOLE																												

NiMo PROJECT

PROPERTY: Rich

HOLE: RI07-02

Easting	Northing	Elev.	Depth (m)
445508	7353769	681	176.79

Contractor: North Star
Drill: MD-002

SURVEY							
Depth (m)	Azimuth	Dip	Method	Depth (m)	Azimuth	Dip	Method
collar	090°	-50°	compass				

Core size: BTW
Casing depth: 21.34 (m) out

Drilling dates: July 15 to 17, 2007

Logged by: D. MacDonald

Target: _____

SUMMARY				
From (m)	To (m)	Interval	Unit	Comments
0.00	24.80	24.80	OSR	Contact heavily weathered/broken
24.80	176.79	151.99	DME	

SAMPLES	
Numbers:	
Total:	
Date sent:	

COMMENTS

NiMo horizon belived to have been intersected in heavily weathered/broken rock near surface.

PROPERTY: RICH **HOLE:** RI07-02

Struct. Type	Struct. Attitude	LITHOLOGY From (m)	To (m)	Interval (m)	Type	Unit	Texture	Modifier	Notes:	ALT.	MINERALS Ca	Sx	Fe	SAMPLES From (m)	To (m)	Interval (m)	Sample	Blocks From (m)	To (m)	Intvl. (m)	GEOTECHNICAL REC (m)	REC Percent	RQD (m)	RQD Percent	Weathering	Hardness	JOINTS Frequency	Attitude	Shape	Roughness	Infilling
BD	70	0.00	24.80	24.80	SHL	DME	LA	BK	calcareous); highly fractured with common limonite staining on fracture surfaces; common quartz veinlets 3 mm wide both parallel to and at high angle to bedding; rare, fg, coarsely bedded silty SS up to 4 cm thick interbedded with BK SHL; SS has slight bioclastic content (15%), unsure of fossil ID.	f			+																								
																		6.10	9.14	3.04	1.01	33	0.00	0	SW	W	30	M	2	3	Li
																		9.14	12.19	3.05	1.34	44	0.00	0	SW	W	30	M	2	2	Li
																		12.19	15.24	3.05	1.83	60	0.00	0	SW	W	30	M	2	2	Li
																		15.24	18.28	3.04	1.03	34	0.00	0	SW	W	30	M	3	3	Li
																		18.28	21.35	3.07	0.70	23	0.00	0	SW	W	30	M	2	2	Li
BD	70	24.80	32.42	7.62	SHL	OSR	LA	BK	24.80 - 32.42 m Finely laminar, non-calcareous BK SHL, more competent than overlying BK SHL, slight increase in hardness;BK SHL interbedded with moderately thick, uncommon, finely laminar GY LST beds (ranging from 10 cm to 60 cm thick) - all the GY LST beds are uniformly silty and fining upwards slightly, but have sharp erosional top and basal contacts - both contacts are 1 - 2 cm wide and vcg with coarsely bedded detrital carbonate (possibly fossiliferous). In general, the GY LST beds decrease in thickness with depth; in the middle of the interval, the BK SHL, although thickly bedded and competent, become softer and more carbonaceous.	w			+																								
																		21.35	24.38	3.03		0		0	SW	W					
																		24.38	27.43	3.05	2.53	83	1.15	38	SW	W	25	60	2	1	Cb
																		27.43	30.48	3.05	3.07	101	2.56	84	FR	MS	7	60	1	1	Cb
																		30.48	33.53	3.05	3.11	102	1.58	52	FR	MS	15	60	1	1	Cb
BD	75	32.42	88.40	55.98	SHL	OSR	LA	BK	32.42 - 88.40 m Finely laminar, thickly bedded, calcareous BK SHL dominant, interbedded with rare, non-calcareous BK SHL beds up to 2.5 m thick; dominant calcareous BK SHL interbedded with rare-to-uncommon, finely laminar GY LST beds ranging from 2 cm (common) to 25 cm (rare) thick, that are mostly silty micrite (to fg sandy silt) with very little (if any) fossil content; common calcite veinlets parallel to BD up to 1 cm thick, and uncommon high	w			+	+	+																						
																		33.53	36.58	3.05	3.08	101	2.24	73	FR	MS	9	60	1	2	Cb
																		36.58	39.62	3.04	2.99	98	1.32	43	FR	MS	14	60	1	1	Cb
																		39.62	42.67	3.05	3.01	99	1.51	50	FR	MS	12	60	1	1	Cb

PROPERTY: RICH **HOLE:** RI07-02

Struct.		LITHOLOGY								ALT.			MINERALS				SAMPLES							Blocks			GEOTECHNICAL						JOINTS					
																											REC		RQD									
Type	Attitude	From (m)	To (m)	Interval (m)	Type	Unit	Texture	Modifier	Notes:				Ca	Sx	Fe		From (m)	To (m)	Interval (m)	Sample				From (m)	To (m)	Intvl. (m)	(m)	Percent	(m)	Percent	Weathering	Hardness	Frequency	Attitude	Shape	Roughness	Infilling	
									angle calcite veinlets 1 mm wide (slight brecciation); rare Sx (Py) bands both parallel to BD and as lenses, showing pinching and swelling also; rare Fe staining along calcite-rich infilled fractures.															42.67	45.72	3.05	3.02	99	1.59	52	FR	MS	9	60	1	2	Cb	
																																					Li
																								45.72	48.77	3.05	3.00	98	1.00	33	FR	MS	25	60	1	1	Cb	
																																					Li
																																					Cb
																								48.77	51.82	3.05	3.08	101	1.15	38	FR	MS	26	60	1	2	Cb	
																																					Li
																								51.82	54.87	3.05	3.05	100	0.86	28	FR	MS	24	60	2	2	Cb	
																								54.87	57.91	3.04	2.89	95	2.21	73	FR	MS	12	60	1	1	Cb	
																								57.91	60.93	3.02	3.00	99	1.79	59	FR	MS	20	60	1	1	Cb	
																								60.93	64.01	3.08	3.04	99	0.81	26	FR	MS	26	60	1	2	Cb	
																								64.01	67.06	3.05	2.88	94	2.65	87	FR	MS	7	60	1	1	Cb	
																								67.06	70.10	3.04	3.00	99	2.48	82	FR	MS	5	60	1	1	Cb	
																								70.10	73.15	3.05	3.06	100	1.58	52	FR	MS	12	60	1	1	Cb	
																								73.15	76.20	3.05	2.99	98	1.89	62	FR	MS	20	60	1	1	Cb	
																								76.20	79.25	3.05	3.10	102	2.78	91	FR	MS	2	5	1	1	Cb	
																								79.25	82.30	3.05	3.04	100	2.19	72	FR	MS	5	5	1	1	Cb	
																								82.30	85.34	3.04	2.96	97	1.78	59	FR	MS	7	60	1	1	Cb	
																								85.34	88.39	3.05	2.87	94	2.19	72	FR	MS	10	60	1	1	Cb	
BD	70	88.40	116.43	28.03	SHL	OSR	LA	BK	BK SHL, moderately thickly bedded (up to 2 m thick), interbedded with common-to-abundant, thin, fg silty-micritic GY LST beds up to 100 cm thick (avg 3 cm); GY LST beds generally fine-upwards - ~ 40% of beds are cg SS and contain bioclastic fragments (crinoids?) up to 1 mm wide; frequency of occurrence of bioclastic-rich beds increases with depth; soft sediment deformation															88.39	91.44	3.05	3.23	106	0.56	18	FR	MS	17	70	1	2	Cb	
																								91.44	94.49	3.05	3.03	99	1.18	39	FR	MS	14	70	1	1	Cb	
																								94.49	97.54	3.05	2.96	97	1.19	39	FR	MS	14	70	1	1	Cb	

PROPERTY: RICH **HOLE:** RI07-02

Struct.		LITHOLOGY								ALT.			MINERALS				SAMPLES							Blocks			GEOTECHNICAL						JOINTS				
																											REC		RQD									
Type	Attitude	From (m)	To (m)	Interval (m)	Type	Unit	Texture	Modifier	Notes:				Ca	Sx	Fe		From (m)	To (m)	Interval (m)	Sample				From (m)	To (m)	Intvl. (m)	(m)	Percent	(m)	Percent	Weathering	Hardness	Frequency	Attitude	Shape	Roughness	Infilling
									present in both the BK SHL and GY LST beds; rare, v dark black carbonaceous SHL beds 1 - 2 cm wide (calcareous and slightly recrystallized)															97.54	100.58	3.04	2.97	98	1.84	61	FR	MS	14	70	1	2	Cb
																								100.58	103.63	3.05	3.05	100	0.73	24	FR	MS	18	60	1	1	Cb
																								103.63	106.68	3.05	3.11	102	1.99	65	FR	MS	13	80	1	1	Cb
																								106.68	109.73	3.05	3.13	103	1.98	65	FR	MS	14	60	1	1	Cb
																								109.73	112.78	3.05	3.12	102	0.86	28	FR	MS	18	60	1	2	Cb
																								112.78	115.83	3.05	3.13	103	1.14	37	FR	MS	19	60	1	1	Cb
BD	70	116.43	135.41	18.98	SHL/L	OSR	LA	BK/	~~116.43 - 135.41 m Finely laminar, black~~ grey calcareous shale interbedded with thickly bedded (10 cm to 3 m) grey limestone (fg silty SS to cg SS) with abundant bioclastic content (perhaps crinoid clasts, up to 1 - 2 mm diam, sub-angular-to-rounded) and generally fining upwards; the thinner GY LST beds have a higher boclastic content than the thicker ones do, and are more crudely bedded than the thicker beds; the more dominant thick GY LST beds are finely laminar, flat to wavy bedded and become more crudely bedded and have erosional contacts at the bases of	w			+															115.83	118.87	3.04	3.05	100	2.19	72	FR	MS	11	50	1	2	Cb
																								118.87	121.92	3.05	2.96	97	1.90	62	FR	MS	13	60	1	2	Cb
																								121.92	124.97	3.05	3.10	102	1.96	64	FR	MS	10	60	1	1	Cb
																								124.97	128.17	3.20	3.02	94	2.19	68	FR	MS	16	60	1	1	Cb
																								128.01	131.06	3.05	3.00	98	1.65	54	FR	MS	6	60	1	2	Cb
																								131.06	134.11	3.05	2.83	93	1.81	59	FR	MS	5	60	2	2	Cb
																								134.11	137.16	3.05	3.08	101	1.95	64	FR	MS	6	60	1	3	Cb
BD	70	135.41	162.08	26.67	SHL	OSR	LA	BK	characteristics as seen in interval 88.40 - 116.43 m, I.e., interbedded calcareous BK SHL with common thin beds of bioclastic GY LST (fg silty SS), with uncommon micritic GY LST mud.	w			+																	137.16	140.21	3.05	3.05	100	1.62	53	FR	MS	10	60	2	3	Cb
																								140.21	143.26	3.05	2.83	93	2.21	72	FR	MS	5	60	1	2	Cb
																								143.26	146.30	3.04	3.02	99	2.31	76	FR	MS	3	30	1	1	Cb
																								146.30	149.30	3.00	3.04	101	2.45	82	FR	MS	4	30	2	2	Cb
																								149.35	150.35	1.00	2.99	299	2.57	257	FR	MS	3	30	1	2	Cb
																								152.40	155.45	3.05	3.07	101	2.20	72	FR	MS	4	60	1	2	Cb

PROPERTY: RICH **HOLE:** RI07-02

Struct.		LITHOLOGY								ALT.			MINERALS				SAMPLES							Blocks			GEOTECHNICAL						JOINTS					
																											REC		RQD									
Type	Attitude	From (m)	To (m)	Interval (m)	Type	Unit	Texture	Modifier	Notes:				Ca	Sx	Fe		From (m)	To (m)	Interval (m)	Sample				From (m)	To (m)	Intvl. (m)	(m)	Percent	(m)	Percent	Weathering	Hardness	Frequency	Attitude	Shape	Roughness	Infilling	
																								155.45	158.50	3.05	3.03	99	2.84	93	FR	MS	1	30	1	1	Cb
																								158.50	161.54	3.04	2.99	98	2.77	91	FR	MS	3	30	2	3	Cb
																								161.54	164.60	3.06	2.97	97	2.53	83	FR	MS	4	60	2	2	Cb
BD	85	162.08	176.79	14.71	SHL	OSR	LA	BK	black calcareous shale, thickly bedded, with rare, thin (3 cm) silty GY LST with no bioclastic content, and diffuse, gradational contacts (0.5 cm), and rare, vfg Sx (Py) banding (3 - 4 mm) parallel to bedding; core fizzes with HCl and yields strong H2S odour.	w			+	+												164.60	167.64	3.04	2.94	97	2.72	89	FR	MS	3	40	1	1	Cb
																								167.64	170.64	3.00	3.05	102	2.52	84	FR	MS	3	60	1	2	Cb
																								170.64	173.43	2.79	2.98	107	2.56	92	FR	MS	2	30	1	1	Cb
		176.79							END OF HOLE															173.43	176.79	3.36	3.04	90	2.61	78	FR	MS	1	30	1	2	Cb

NiMo PROJECT

PROPERTY: Rich

HOLE: RI07-04

Easting	Northing	Elev.	Depth (m)
445280	7354545		48.77

Contractor: North Star
Drill: MD-002

SURVEY							
Depth (m)	Azimuth	Dip	Method	Depth (m)	Azimuth	Dip	Method
collar	090°	-50°	compass				

Core size: BTW
Cassing depth: 17.09 (m) out

Drilling dates: July 18 to 19, 2007

Logged by: D. MacDonald

Target: _____

SUMMARY				
From (m)	To (m)	Interval	Unit	Coments
0.00	12.19	12.19	OVB	
12.19	48.77	36.58	OSR?	DME?

SAMPLES	
Numbers:	
Total:	
Date sent:	

COMMENTS

PROPERTY: RICH **HOLE:** RI07-04

Struct.		LITHOLOGY								ALT.			MINERALS				SAMPLES							Blocks			GEOTECHNICAL						JOINTS					
																											REC		RQD									
Type	Attitude	From (m)	To (m)	Interval (m)	Type	Unit	Texture	Modifier	Notes:								From (m)	To (m)	Interval (m)	Sample				From (m)	To (m)	Intvl. (m)	(m)	Percent	(m)	Percent	Weathering	Hardness	Frequency	Attitude	Shape	Roughness	Infilling	
		0.00	12.19	12.19	OB				0 - 12.19 m Overburden																												
																								12.00	12.19	0.19	0.19	100	0.00	0	MW	W	30	M			
		12.19	48.77	36.58	SHL	OSR	FX	EA	12.19 - 18.50 m Highly friable, compacted, sandy black clay, poorly lithified and highly fractured. Too weathered to discern	ex							12.19	15.24	3.05					12.19	15.24	3.05	1.23	40	0.00	0	EW	VW	30	M			
																								15.24	18.28	3.04	1.60	53	0.00	0	EW	VW	30	M			
																								18.28	21.35	3.07	1.33	43	0.00	0	HW	VW	30	60			
BD	80				SHL	OSR	LA/I	BK/	18.50 - 21.94 m Highly fissile and moderately friable laminar BK SHL with abundant fractures; BK SHL slightly more competent than in previous interval.	ex																													
																								21.35	24.38	3.03	0.87	29	0.00	0	HW	VW	30	M			
BD	80				SHL	OSR	FX	GY	altered BK SHL; highly fractured with common limonite from 31.20 - 34.02 m; mostly earthy and crumbles under light hand pressure; after about the 34 m mark, SHL becomes darker and even more earthy in texture, until the core is reduced to black, clayey sand by about the 39 m mark until the EOH (48.77 m).	ex																																	
																								24.38	27.43	3.05	0.43	14	0.00	0	HW	VW	30	M			
																								27.43	30.48	3.05	0.55	18	0.00	0	HW	VW	30	M			
																								30.48	33.53	3.05	1.20	39	0.00	0	HW	VW	30	M			Li
																								33.53	36.58	3.05	2.47	81	0.00	0	HW	VW	30	M			Li
																								36.58	39.62	3.04	1.60	53	0.00	0	HW	VW	30	M			
																								39.62	42.67	3.05	0.55	18	0.00	0	EW	VW	30	M			
																								42.67	45.72	3.05	0.38	12	0.00	0	EW	VW	30	M			
		48.77							END OF HOLE															45.72	48.77	3.05	0.75	25	0.00	0	EW	VW	30	M			

NiMo PROJECT

PROPERTY: RICH

HOLE: RI07-05

Easting	Northing	Elev.	Depth (m)
444169	7356993	614	201.17

Contractor: North Star
Drill: MD-002

SURVEY							
Depth (m)	Azimuth	Dip	Method	Depth (m)	Azimuth	Dip	Method
collar	070°	-60°	compass				

Core size: BTW
Casing depth: 9.14 (m) out

Drilling dates: July 19 to 21, 2007

Logged by: D. MacDonald

Target: _____

SUMMARY				
From (m)	To (m)	Interval	Unit	Comments
0	6.69	6.69	OVB	
6.69	152.56	145.87	DME	
152.56	152.57	0.01	NiMo	
152.57	201.17	48.6	OSR	

SAMPLES

Numbers: C385566 - C385582

Total: 17
Date sent: August 2, 2007

COMMENTS

PROPERTY: RICH **HOLE:** RI07-05

Struct. Type	Struct. Attitude	LITHOLOGY From (m)	To (m)	Interval (m)	Type	Unit	Texture	Modifier	Notes:	ALT.	MINERALS Ca	Sx	Fe	SAMPLES From (m)	To (m)	Interval (m)	Sample	Ni (ppm)	Zn (ppm)	Mo (ppm)	Blocks From (m)	To (m)	Intvl. (m)	GEOTECHNICAL REC (m)	REC Percent	RQD (m)	RQD Percent	Weathering	Hardness	JOINTS Frequency	Attitude	Shape	Roughness	Infilling
		0.00	6.69	6.69	OVB																												
BD	80	6.69	152.56	145.87	SHL	DME	FX	BK	6.69 - 27.68 m Highly fissile and friable, finely laminar BK SHL, strongly altered physically, with common limonite staining on fracture surfaces over first 7 m and becoming less common until about the 21 m mark; @ 21+ m, white, vfg, powdery alteration product common on fracture surfaces; rare 30 cm thick zones v highly altered and clay-rich BK SHL that breaks up easily in the hand.	s			+										8.69	9.14	0.45	0.45	100	0.00	0	MW	VW	30	90	3	2	Li
																					9.14	12.19	3.05	1.91	63	0.00	0	MW	VW	30	90	3	2	Li
																					12.19	15.24	3.05	1.61	53	0.00	0	MW	VW	30	90	2	2	Li
																					15.24	18.28	3.04	0.93	31	0.00	0	MW	W	30	90	2	2	GYP
																					18.28	21.35	3.07	2.18	71	0.00	0	MW	W	30	90	2	2	GYP
																					21.35	24.38	3.03	0.54	18	0.00	0	SW	MS	30	90	2	2	GYP
																					24.38	27.43	3.05	1.34	44	0.00	0	SW	MS	30	90	2	2	GYP
BD	85				SHL	DME	LA	BK	27.68 - 85.60 m In general, finely laminar, moderately fissile, flat-bedded BK SHL that increases inhardness and competence relative to the BK SHL in the previous interva (specifics to follow at appropriate intervals); rare-to-uncommon, finely laminar, thin GY LST interbedded with BK SHL, and are silty to vfg SS and fine upwards generally; rare, high-angle calcite + quartz-rich veinlets, and rare calcite veinlets parallel to BD; uncommon Sx blebs (1 - 2 mm wide) and bands (up to 2 mm wide) rare at top of interval and becoming more common with depth; uncommon-to-common GY siliceous silts interbedded with BK SHL, and said silts increase in grainsize with depth; sulfides (Py) that are common in blebs/small lenses are fg - vfg crystalline.	w			+	+									27.43	30.48	3.05	1.45	48	0.00	0	FR	MS	20	90	2	2	GYP
																					30.48	33.53	3.05	1.76	58	0.00	0	FR	MS	20	80	2	2	GYP
																					33.53	36.58	3.05	2.87	94	0.00	0	FR	MS	20	80	2	2	GYP
																					36.58	39.62	3.04	2.53	83	0.33	11	FR	MS	15	80	2	2	GYP
																					39.62	42.67	3.05	2.93	96	0.00	0	FR	MS	15	80	2	2	GYP
																					42.67	45.72	3.05	2.69	88	0.00	0	FR	MS	12	80	2	2	GYP
																					45.72	48.77	3.05	3.05	100	0.10	3	FR	MS	15	80	2	2	ALS
																					48.77	51.82	3.05	2.86	94	0.30	10	FR	MS	20	80	2	2	ALS
																					51.82	54.87	3.05	3.09	101	0.14	5	FR	MS	17	80	2	2	ALS
																					54.87	57.91	3.04	2.94	97	0.41	13	FR	S	18	80	2	2	GYP
																					57.91	60.93	3.02	3.08	102	0.56	19	FR	S	15	80	2	2	GYP
																					60.93	64.01	3.08	2.89	94	0.36	12	FR	S	15	80	2	2	ALS
																					64.01	67.06	3.05	3.03	99	0.40	13	FR	MS	15	80	2	2	GYP
																					67.06	70.10	3.04	2.93	96	0.84	28	FR	MS	12	80	2	2	GYP

PROPERTY: RICH **HOLE:** RI07-05

Struct. Type	Struct. Attitude	LITHOLOGY From (m)	LITHOLOGY To (m)	LITHOLOGY Interval (m)	LITHOLOGY Type	LITHOLOGY Unit	LITHOLOGY Texture	LITHOLOGY Modifier	Notes:	ALT.			MINERALS Ca	MINERALS Sx	MINERALS Fe		SAMPLES From (m)	SAMPLES To (m)	SAMPLES Interval (m)	SAMPLES Sample	SAMPLES Ni (ppm)	SAMPLES Zn (ppm)	SAMPLES Mo (ppm)	Blocks From (m)	Blocks To (m)	Blocks Intvl. (m)	GEOTECHNICAL REC (m)	GEOTECHNICAL REC Percent	GEOTECHNICAL RQD (m)	GEOTECHNICAL RQD Percent	GEOTECHNICAL Weathering	GEOTECHNICAL Hardness	JOINTS Frequency	JOINTS Attitude	JOINTS Shape	JOINTS Roughness	JOINTS Infilling
																									70.10	73.15	3.05	3.08	101	0.58	19	FR	MS	10	80	2	2	GYP
																									73.15	76.20	3.05	2.98	98	2.16	71	FR	MS	3	80	2	2	GYP
																									76.20	79.25	3.05	3.07	101	0.75	25	FR	MS	8	75	1	2	Cb
CN					LST	DME	CN	GY	77.65 - 77.71 m Concentrically layered LST concretion 6 cm in diam. That incorporates surrounding BK SHL into itself in a 'liesegang' manner.	w			+																												
BD	85				LST	DME	LA	GY	massive GY silt-sandy silt LST, fining upwards slightly	w			+											79.25	82.30	3.05	2.99	98	1.17	38	FR	MS	10	75	1	1	GYP
BD	80				LST	DME	LA	GY	80.58 - 80.66 m v slightly grey, silty LST that is finely laminar	w			+																										
BD	85				SHL	DME	LA	BK	81.96 - 82.20 m Finely laminar, calcareous BK SHL bed.	w			+																												
																									82.30	85.34	3.04	2.83	93	0.80	26	FR	MS	7	90	1	1	GYP
BD	85				LST	DME	LA	GY	85.60 - 87.88 m Thick subunit of generally finely laminar, flat-to-wavy bedded GY LST with alternating light GY (silty-to-sandy silt) + darker GY beds from 2 cm to 40 - 50 cm thick; some erosional contacts internally over 5 cm, and rare soft-sediment slumping; uncommon fg flecks of Py in disrupted/slightly bioturbated zone about 1 m into the interval; several fining upwards cycles	w			+	+										85.34	88.39	3.05	3.05	100	2.25	74	FR	MS	4	90	1	1	Cb
BD	80				LST	DME	LA	GY	87.88 - 88.30 m Mostly fg GY silty LST, flatly-bedded, thinly laminar, inerbedded with rare, calcareous, finely laminar BK SHL and non-calcareous BK SHL beds up to 10 cm thick; GY LST is slightly internally brecciated (calcite matri, mostly angular clasts; matrix up to 3 cm wide nd generally parallel to BD)	w			+	+																												
BD	70-65				SHL	DME	LA	BK	88.30 - 97.50 m Finely laminar, GY-BK SHL (flat-bedded mostly) with abundant calcite-rich veinlets both parallel (dominant) and almost perpendicular (less dominant) to BD; rare, small zones (10 cm wide) of localized brecciation by calcite veinlets up to 3 mm wide. BD angle becomes gradually steeper (up to 60 degrees) with depth in this interval.	w			+	+										88.39	91.44	3.05	3.04	100	0.25	8	FR	MS	8	75	1	1	GYP
																									91.44	94.49	3.05	3.01	99	3.01	99	FR	MS	10	75	1	1	GYP
																									94.49	97.54	3.05	2.76	90	0.14	5	FR	MS	11	65	1	1	GYP
BD	60				LST	DME	LA	GY	97.50 - 97.93 m Finely laminar, flat-bedded, silty GY LST, with fairly uniform teture throughout, almost massive.	w			+																										
BD	60 - 80				SHL	DME	LA	BK		w			+	+																								
																									97.54	100.58	3.04	2.93	96	0.87	29	FR	MS	13	50	1	1	GYP
																									100.58	103.63	3.05	2.75	90	0.11	4	FR	MS	12	80	1	1	GYP
									97.93 - 152.56 m BK-GY, finely laminar, flat-bedded SHL interbedded with slightly lighter GY, fg non-calcareous silt and rare, finely laminar, GY LST beds (up to 4 cm wide), with both sharp and diffuse contacts with surrounding shales; BK SHL beds and GY non-calcareous silt beds alternate about every 5 cm or so over the whole interval; rare-to-common Sx blebs (up to 1 cm x 1 cm) and both contorted and flatly laminar vfg bands up to 2 cm wide that increase in																																		
																									103.63	106.68	3.05	3.05	100	0.63	21	FR	MS	12	80	1	1	GYP
																									106.68	109.73	3.05	3.01	99	0.94	31	FR	MS	9	80	1	1	GYP
																									109.73	112.78	3.05	3.02	99	0.60	20	FR	MS	7	80	1	1	GYP

PROPERTY: RICH **HOLE:** RI07-05

Struct. Type	Struct. Attitude	LITHOLOGY From (m)	To (m)	Interval (m)	Type	Unit	Texture	Modifier	Notes:	ALT.	MINERALS Ca	Sx	Fe	SAMPLES From (m)	To (m)	Interval (m)	Sample	Ni (ppm)	Zn (ppm)	Mo (ppm)	Blocks From (m)	To (m)	Intvl. (m)	GEOTECHNICAL REC (m)	REC Percent	RQD (m)	RQD Percent	Weathering	Hardness	JOINTS Frequency	Attitude	Shape	Roughness	Infilling
									abundance with depth; BD angle shifts from 60 degrees to 85 degrees at about 101 m mark; intensely abundant calcite veinlets (up to 0.5 cm wide both parallel and perpendicular to BD in first 3 m of interval; calcite veinlets become rare over the 101 - 119.5 m interval, and becoming mostly parallel to BD; from 119 - 152 m, calcite-rich veinlets are common and mostly parallel to BD, with small (10 -15 cm wide) localized zones of brecciation (angular clasts 1 cm x 2 cm, calcite matrix) at 118.35 - 118.40 m, and 127.60 - 127.75 m.																																	
																					112.78	115.83	3.05	3.01	99	0.12	4	FR	MS	9	80	1	1	GYP
																					115.83	118.87	3.04	2.86	94	0.78	26	FR	S	6	80	1	1	GYP
																					118.87	121.92	3.05	3.00	98	1.26	41	FR	S	6	80	1	1	GYP
																					121.92	124.97	3.05	3.03	99	0.00	0	FR	S	13	80	2	2	GYP
																					124.97	128.17	3.20	3.08	96	1.63	51	FR	MS	6	80	3	3	GYP
																					128.01	131.06	3.05	2.87	94	1.48	49	FR	MS	7	80	1	1	GYP
																					131.06	134.11	3.05	3.08	101	1.12	37	FR	MS	6	80	1	1	GYP
																					134.11	137.16	3.05	3.04	100	1.22	40	FR	MS	5	85	1	1	GYP
																					137.16	140.21	3.05	3.05	100	1.45	48	FR	MS	5	80	1	1	GYP
																					140.21	143.26	3.05	3.03	99	1.75	57	FR	MS	7	80	1	1	GYP
																					143.26	146.30	3.04	3.04	100	0.99	33	FR	MS	9	80	1	1	GYP
														144.76	146.26	1.50	C385566	121.0	895	40.3													
														146.26	147.76	1.50	C385567	127.0	667	44.2													
														147.76	149.26	1.50	C385568	179.0	893	60.3	146.30	149.30	3.00	3.05	102	0.71	24	FR	MS	7	80	1	1	GYP
														149.26	150.26	1.00	C385569	155.0	261	49.3													
														150.26	151.26	1.00	C385570	158.0	252	49.7													
														151.26	151.76	0.50	C385571	172.5	206	46.2	149.35	150.35	1.00	2.85	285	0.30	30	FR	MS	12	75	1	1	GYP
														151.76	152.26	0.50	C385572	156.0	317	49.3													
														152.26	152.56	0.30	C385573	413.0	591	81.8													
BD	80	152.56	152.57	0.01	SX	NIMO	LA	BZ	152.56 - 152.575 m Bronze, thinly, wavy laminar sulfides, thinly bedded with mild bioturbation, slight calcite content	w	+	+		152.56	152.58	0.01	C385574	3.90%	4.25%	714	152.40	155.45	3.05	2.94	96	1.03	34	FR	MS	30	80	2	1	Cb
BD	80	152.58	201.17	48.59	SHL	OSR	LA	BK	152.58 - 210.17 m Interval starts with finely laminar, flatly bedded non-calcareous BK SHL, which becomes dominantly calcareous after the 155.01 m mark, and I interbedded with common, finely laminar, flat-bedded, mostly micritic, silty GY LST, which LSTs have both gradational and sharp boundaries (both conformable to BK SHL); BK SHL becomes slightly darker with depth and more uniform in texture overall; common Sx (Py) lenses (1 cm x 2 cm) and beds up to 3 cm thick, commonly with wavy laminar tops; rare, calcite-rich veinlets parallel to BD; GY LST beds decrease in abundance with depth, with the exception of a 1 m thick GY LST bed at 189 m; rare calcite veinlets mostly at high angles to bedding; disseminated Sx is prevalent over last 15 m of hole; starting at about 184.22 m, the GY LST beds are a bit coarser grained (fg silty SS); thin, laminar, fg silty SS beds that average 1 - 3 cm thick with crude, low-angle X-bedding become more abundant near the	w	+	+		152.58	152.88	0.30	C385575	197.5	431	46.2											
														152.88	153.38	0.50	C385576	151.5	302	54.5													
														153.38	153.88	0.50	C385577	166.5	234	56.2	155.45	158.50	3.05	3.11	102	3.03	99	FR	MS	4	10	2	2	Cb
														153.88	154.88	1.00	C385578	190.0	200	60.6													
														154.88	155.88	1.00	C385579	113.5	325	35.3													
														155.88	157.38	1.50	C385580	108.0	336	31.8	158.50	161.54	3.04	3.12	103	2.82	93	FR	MS	6	75	2	2	Cb
														157.38	158.88	1.50	C385581	122.5	244	36.4													
														158.88	160.38	1.50	C385582	133.0	266	38.5													
																					161.54	164.60	3.06	2.79	91	2.42	79	FR	MS	7	80	2	2	Cb
																					164.60	167.64	3.04	3.10	102	3.09	102	FR	MS	0				
																					167.64	170.64	3.00	3.02	101	3.01	100	FR	MS	1	5	1	2	Cb
																					170.64	173.43	2.79	3.10	111	3.04	109	FR	MS	1	5	1	2	Cb
																					173.74	176.78	3.04	2.90	95	2.41	79	FR	MS	3	5	2	2	Cb
																					176.78	179.83	3.05	2.93	96	2.79	91	FR	MS	2	5	2	2	Cb

PROPERTY: RICH **HOLE:** RI07-05

Struct.		LITHOLOGY								ALT.			MINERALS				SAMPLES								Blocks			GEOTECHNICAL						JOINTS				
																												REC		RQD									
Type	Attitude	From (m)	To (m)	Interval (m)	Type	Unit	Texture	Modifier	Notes:				Ca	Sx	Fe		From (m)	To (m)	Interval (m)	Sample	Ni (ppm)	Zn (ppm)	Mo (ppm)		From (m)	To (m)	Intvl. (m)	(m)	Percent	(m)	Percent	Weathering	Hardness	Frequency	Attitude	Shape	Roughness	Infilling
									EOH (i.e., thicker SS beds become less common). EOH																179.83	182.88	3.05	3.11	102	2.95	97	FR	MS	1	5	1	1	Cb
																									182.88	185.93	3.05	2.84	93	2.65	87	FR	MS	1	40	1	1	GYP
																									185.93	188.98	3.05	3.09	101	1.26	41	FR	MS	4	20	3	1	Cb
																									188.98	192.02	3.04	3.13	103	1.81	60	FR	MS	3	30	1	1	Cb
																									192.02	195.07	3.05	2.97	97	1.24	41	FR	MS	3	30	3	2	Cb
																									195.07	198.12	3.05	3.11	102	2.64	87	FR	MS	3	20	1	1	Cb
		201.17							END OF HOLE																198.12	201.17	3.05	2.99	98	2.22	73	FR	MS	2	25	1	1	Cb

NiMo PROJECT

PROPERTY: Rich

HOLE: RI07-06

Easting	Northing	Elev.	Depth (m)
444099	7357286	622	131.06

Contractor: North Star
Drill: MD-001

Core size: BTW
Casing depth: 15.24 (m) out

Drilling dates: July 19 to 21, 2007

Logged by: D. MacDonald

Target: _____

SURVEY

Depth (m)	Azimuth	Dip	Method	Depth (m)	Azimuth	Dip	Method
collar	070°	-75°	compass				

SUMMARY

From (m)	To (m)	Interval	Unit	Comments
0.00	15.20	15.20	OVB	
15.20	58.62	43.42	DME	
58.62	58.66	0.04	NiMo	
58.66	131.06	72.40	OSR	

SAMPLES

Numbers: C488171 - C488200

Total: 30
Date sent: August 12, 2007

COMMENTS

Drillers inserted extra block, 10' discrepancy from drillers time sheets

NiMo PROJECT

PROPERTY: Rich

HOLE: RI07-07

Easting	Northing	Elev.	Depth (m)
444283	7356805	621	27.43

Contractor: North Star
Drill: MD-002

SURVEY							
Depth (m)	Azimuth	Dip	Method	Depth (m)	Azimuth	Dip	Method
collar	070°	-60°	compass				

Core size: BTW
Casing depth: (m) out

Drilling dates: July 21, 2007

Logged by: D. Macdonald

Target:

SUMMARY				
From (m)	To (m)	Interval	Unit	Comments
0.00	12.19	12.19	OVB	
12.19	27.43	15.24	DME	

SAMPLES

Numbers:

Total: 0
Date sent:

COMMENTS

Pad sinking, hole aborted and restarted as RI07-07a

PROPERTY: RICH **HOLE:** RI07-07

Struct.		LITHOLOGY								ALT.			MINERALS				SAMPLES							Blocks			GEOTECHNICAL						JOINTS					
																											REC		RQD									
Type	Attitude	From (m)	To (m)	Interval (m)	Type	Unit	Texture	Modifier	Notes:				Ca	Sx	Fe		From (m)	To (m)	Interval (m)	Sample				From (m)	To (m)	Intvl. (m)	(m)	Percent	(m)	Percent	Weathering	Hardness	Frequency	Attitude	Shape	Roughness	Infilling
		0.00	12.19	12.19	OVB				Overburden + black sand																												
		12.19	27.43	15.24	SHL	DME	EA	BK	12.19 - 18.50 m Highly weathered, poorly lithified, earthy, highly friable, BK SHL - too weathered to discern structures	ex														12.19	15.24	3.05	0.50	16	0.00	0	EW	VW					
																								15.24	18.28	3.04	1.84	61	0.00	0	HW	VW					
																								18.28	21.35	3.07	0.44	14	0.00	0	HW	VW					
BD	85				SHL	DME	LA	BK	18.50 - 27.43 m Highly fissile and friable BK SHL that is earthy for the first 8 m of the interval, and becomes slightly more competent in the last metre of the interval. EOH	m-s																												
																								21.35	24.38	3.03	1.16	38	0.00	0	HW	VW					
		27.43							END OF HOLE															24.38	27.43	3.05	0.85	28	0.00	0	MW	W	30	90	1	1	ALS

NiMo PROJECT

PROPERTY: Rich

HOLE: RI07-07a

Easting	Northing	Elev.	Depth (m)
444283	7356805	621	170.69

Contractor: North Star
Drill: MD-002

SURVEY							
Depth (m)	Azimuth	Dip	Method	Depth (m)	Azimuth	Dip	Method
collar	070°	-60°	compass				

Core size: BTW
Casing depth: 24.38 (m) out

Drilling dates: July 21 to July 23, 2007

Logged by: D. MacDonald

Target: Realigned drill, restarted RI07-07

SUMMARY				
From (m)	To (m)	Interval	Unit	Comments
0.00	24.38	24.38	OVB	
24.38	158.64	134.26	DME	
158.64	158.67	0.03	NiMo	
158.67	170.69	12.02	OSR	

SAMPLES	
Numbers:	C385589 - C385600
	C488151 - C488170
Total:	32
Date sent:	August 2, 2007

COMMENTS

PROPERTY: RICH **HOLE:** RI07-07A

Struct. Type	Struct. Attitude	LITHOLOGY From (m)	To (m)	Interval (m)	Type	Unit	Texture	Modifier	Notes:	ALT.	MINERALS Ca	Sx	Fe	SAMPLES From (m)	To (m)	Interval (m)	Sample	Ni (ppm)	Zn (ppm)	Mo (ppm)	Blocks From (m)	To (m)	Intvl. (m)	GEOTECHNICAL REC (m)	REC Percent	RQD (m)	RQD Percent	Weathering	Hardness	JOINTS Frequency	Attitude	Shape	Roughness	Infilling
		0.00	24.38	24.38	OVB				Overburden																								
BD	85	24.38	67.10	42.72	SHL	DME	LA	BK	24.38 - 67.10 m Highly fissile and somewhat friable finely laminar, flat-bedded black shale with moderately abundant fractures that are commonly coated with limonite in the first 10 metres; moderately weathered from 24.38 - 35.62 m, becoming slightly more competent over remainder of interval. Common-to-abundant SX (Py) bands (up to 0.5 cm thick) and blebby lenses (1 mm x 3 mm) - banding and blebs flatly-bedded, parallel to BD; black shale interbedded with abundant grey, fg silts that exhibit rare X-stratification. Two fining-upward cycles in this interval, 24.38 - 41.50 m and 41.50 - 67.10 m; both cycles comprise dominant BK SHL (finely laminar, flat-bedded) interbedded with fg grey, siliceous silts, with the upper 1/2 of each cycle dominated by BK SHL, with GY SLT becoming more common in latter half of each cycle. BK SHL beds average 30+ cm, whereas GY SLT beds average 4 - 5 cm. Uncommon-to-common veinlets ~2mm wide, parallel to BD increase in abundance at end of interval. Interval ends in bitumen-rich layer about 5 cm thick.	m		+	+													24.38	27.43	3.05	2.56	84	0.00	0	HW	W	30	90	1	2	GYP
																					27.43	30.48	3.05	2.92	96	0.00	0	MW	W	30	60	1	1	GYP
																					30.48	33.53	3.05	2.84	93	0.00	0	MW	W	30	90	1	1	ALS
																					33.53	36.58	3.05	2.81	92	0.00	0	MW	W	30	90	1	2	GYP
																					36.58	39.62	3.04	3.00	99	0.00	0	SW	MS	30	90	1	1	GYP
																					39.62	42.67	3.05	3.10	102	0.00	0	SW	MS	20	85	1	1	GYP
																					42.67	45.72	3.05	2.99	98	0.35	11	FR	MS	20	85	1	2	GYP
																					45.72	48.77	3.05	3.03	99	0.00	0	FR	MS	10	90	2	2	GYP
																					48.77	51.82	3.05	2.96	97	0.39	13	FR	MS	10	90	2	1	GYP
																					51.82	54.87	3.05	3.00	98	0.10	3	FR	MS	15	90	1	2	GYP
																					54.87	57.91	3.04	3.04	100	0.00	0	FR	MS	15	85	1	2	GYP
																					57.91	60.93	3.02	3.04	101	0.00	0	FR	MS	20	90	2	2	GYP
																					60.93	64.01	3.08	3.04	99	0.10	3	FR	MS	20	85	1	2	GYP

PROPERTY: RICH **HOLE:** RI07-07A

Struct.		LITHOLOGY								ALT.			MINERALS			SAMPLES							Blocks			GEOTECHNICAL						JOINTS				
																											REC		RQD								
Type	Attitude	From (m)	To (m)	Interval (m)	Type	Unit	Texture	Modifier	Notes:				Ca	Sx	Fe	From (m)	To (m)	Interval (m)	Sample	Ni (ppm)	Zn (ppm)	Mo (ppm)	From (m)	To (m)	Intvl. (m)	(m)	Percent	(m)	Percent	Weathering	Hardness	Frequency	Attitude	Shape	Roughness	Infilling
																							64.01	67.06	3.05	2.98	98	0.32	10	FR	MS	20	90	1	1	GYP
BD	85				LST	DME	LA	GY	67.10 - 69.85 m Finely-to-medium bedded, flat-to-wavy laminar grey, sandy silt, with uncommon X-stratification - sharp upper contact, lower contact obscured by brecciation; overall, interval is coarsening upwards; interval is severely brecciated at about the 69 m mark, as is the last 40 cm of the interval; the breccia comprises angular GY LST clasts floating in a calcite matrix 3 cm across at widest point.	w			+												67.06	70.10	3.04	3.05	100	2.28	75	FR	MS	5	60	2	2	GYP
BD	80				SHL	DME	LA	GY		w			+	+										70.10	73.15	3.05	3.04	100	0.58	19	FR	MS	15	45	2	2	GYP
									69.85 - 82.20 m Interval starts with finely laminar black shale (dominant) interbedded with finely flatly-to-wavy laminar, silty grey limestone; common nodular and bands of Py up to 2 mm thick, parallel to BD; rare, thick, coarsening downward GY LST beds up to 15 cm thick.													73.15	76.20	3.05	3.10	102	0.48	16	FR	MS	8	30	1	1	GYP
																							76.20	79.25	3.05	2.97	97	1.81	59	FR	MS	5	30	2	1	Cb
																							79.25	82.30	3.05	3.11	102	1.61	53	FR	MS	6	85	1	3	Cb
BD	85				SHL	DME	LA	BK		w				+																						
									82.20 - 86.71 m Finely laminar black shale with uncommon Py blebs (2mm x 2mm); BK SHL interbedded with rare, grey, siliceous FG silt beds up to 3 cm thick													82.30	85.34	3.04	2.95	97	2.38	78	FR	MS	2	85	2	3	Cb
																							85.34	88.39	3.05	3.08	101	2.35	77	FR	MS	2	60	1	2	Cb
BD	80				LST	DME	LA	GY	86.71 - 87.50 m Finely laminar, flat-bedded, grey, silty limestone that fines downward into micritic mud; fairly uniform in texture throughout.	w			+																										
BD	85				SHL	DME	LA	BK		w				+																						
									87.50 - 96.78 m Finely laminar, black shale (flat-bedded) interbedded with grey, siliceous silt (finely laminar, flat-bedded), with common Sx (Py) bands and blebs, parallel to BD.													88.39	91.44	3.05	3.05	100	2.45	80	FR	MS	3	30	2	2	Cb
																							91.44	94.49	3.05	3.07	101	2.13	70	FR	MS	2	85	1	1	GYP
																95.88	96.18	0.30	C385589	113.5	155	50.8														
																96.18	96.48	0.30	C385590	64.4	77	25.6	94.49	97.54	3.05	2.97	97	2.35	77	FR	MS	3	30	1	3	Cb
																96.48	96.78	0.30	C385591	193.0	273	77.7														
BD	85				SX	DME	LA	BZ	96.78 - 96.81 m NIMO-esque 'unit' (?) with finely, wavy laminar bedded sulfides (gold-bronze, but not quite the same as NIMO horizon).	w					+						96.78	96.81	0.03	C385592	1500	1600	360														
BD	85				SHL	DME	LA	BK		w			+	+		96.81	97.11	0.30	C385594	112.0	98	44.5	97.54	100.58	3.04	3.01	99	1.89	62	FR	MS	5	85	1	1	Cb
																97.11	97.41	0.30	C385595	122.0	178	39.9														

PROPERTY: RICH **HOLE:** RI07-07A

Struct. Type	Struct. Attitude	LITHOLOGY From (m)	LITHOLOGY To (m)	LITHOLOGY Interval (m)	LITHOLOGY Type	LITHOLOGY Unit	LITHOLOGY Texture	LITHOLOGY Modifier	Notes:	ALT.			MINERALS Ca	MINERALS Sx	MINERALS Fe		SAMPLES From (m)	SAMPLES To (m)	SAMPLES Interval (m)	SAMPLES Sample	SAMPLES Ni (ppm)	SAMPLES Zn (ppm)	SAMPLES Mo (ppm)	Blocks From (m)	Blocks To (m)	Blocks Intvl. (m)	GEOTECHNICAL REC (m)	GEOTECHNICAL REC Percent	GEOTECHNICAL RQD (m)	GEOTECHNICAL RQD Percent	GEOTECHNICAL Weathering	GEOTECHNICAL Hardness	JOINTS Frequency	JOINTS Attitude	JOINTS Shape	JOINTS Roughness	JOINTS Infilling
																	97.41	97.71	0.30	C385597	104.5	224	33.7															
																								100.58	103.63	3.05	3.04	100	2.44	80	FR	MS	3	60	1	1	GYP
									96.81 - 158.67 m Interval starts with finely laminar, flat-bedded black shale (generally with beds 3 - 10 cm thick), interbedded with finely laminar, grey silt (flat-to-slightly-wavily bedded); interval shows coarsening downward in general, for bth the BK SHL and GY SLT, until about 146.10 m, where both the SHL and SLT become more fine-grained, and the interbeddedness becomes finer. In general, the abundance of Sx (Py) banding and nodules decreases with depth and are almost absent by end of interval; small zones of brecciation and veining (calcite) are common from about 135.32 m onwards (veinlets range from 1mm - 1cm wide and are parallel to BD) and decrease slightly in abundance by 165 m. Last 2.5 - 3.5 m is pure, non-lithified mud, poor recovery.								BLANK			C385593	1.0	16	0.37																	
																	BLANK			C385596	2.4	16	0.19														
																								103.63	106.68	3.05	3.05	100	2.61	86	FR	MS	2	85	1	1	Cb
																								106.68	109.73	3.05	2.98	98	2.13	70	FR	MS	3	85	1	1	Cb
																								109.73	112.78	3.05	3.11	102	2.36	77	FR	MS	3	85	1	1	GYP
																								112.78	115.83	3.05	3.04	100	2.60	85	FR	MS	3	85	1	1	GYP
																								115.83	118.87	3.04	3.08	101	2.25	74	FR	MS	4	85	1	1	Cb
																								118.87	121.92	3.05	3.09	101	2.35	77	FR	MS	4	85	1	1	Cb
																								121.92	124.97	3.05	2.94	96	2.57	84	FR	MS	2	85	1	1	GYP
																								124.97	128.17	3.20	3.08	96	2.76	86	FR	MS	2	85	1	1	Cb
																								128.01	131.06	3.05	3.04	100	1.75	57	FR	MS	7	80	1	1	Cb
																								131.06	134.11	3.05	3.06	100	1.67	55	FR	MS	7	80	1	1	Cb
																								134.11	137.16	3.05	3.08	101	1.20	39	FR	MS	6	80	1	1	Cb
																								137.16	140.21	3.05	3.13	103	0.52	17	FR	MS	10	85	1	1	Cb
																	BLANK			C488151	3.3	20	0.44														
																	BLANK			C488159	2.9	16	0.26	140.21	143.26	3.05	3.11	102	0.90	30	FR	MS	12	80	1	1	Cb
																								143.26	146.30	3.04	2.98	98	1.11	37	FR	MS	12	80	1	1	Cb
																								146.30	149.30	3.00	3.11	104	1.61	54	FR	MS	11	80	1	1	Cb
																	148.26	149.76	1.50	C385598	136.5	546	50.0														
																	149.76	151.26	1.50	C385599	123.5	809	38.2	149.35	150.35	1.00	2.89	289	1.10	110	FR	MS	12	80	2	2	Cb
																	151.26	152.26	1.00	C385600	129.0	693	44.7														
																	152.26	153.26	1.00	C488152	131.0	607	38.0														
																	153.26	154.26	1.00	C488153	121.5	239	35.4	152.40	155.45	3.05	2.82	92	1.24	41	FR	MS	11	85	1	1	Cb
																	154.26	154.76	0.50	C488154	146.0	240	42.0														
																	154.76	155.26	0.50	C488155	211.0	234	50.7														

PROPERTY: RICH **HOLE:** RI07-07A

Struct.		LITHOLOGY								ALT.			MINERALS			SAMPLES							Blocks			GEOTECHNICAL						JOINTS				
																										REC		RQD									
Type	Attitude	From (m)	To (m)	Interval (m)	Type	Unit	Texture	Modifier	Notes:				Ca	Sx	Fe	From (m)	To (m)	Interval (m)	Sample	Ni (ppm)	Zn (ppm)	Mo (ppm)	From (m)	To (m)	Intvl. (m)	(m)	Percent	(m)	Percent	Weathering	Hardness	Frequency	Attitude	Shape	Roughness	Infilling
																155.26	158.63	3.37	C488156	105.0	125	28.8	155.45	158.50	3.05	0.84	28	0.00	0	FR	MS					
																158.63	158.64	0.01	C488157	190.5	448	44.8														
BD	85	158.64	158.67	0.03	SX	NIMO	LA	BZ	158.64 - 158.67 m Finely laminar, bronze sulfide bands showing mild bioturbation (laminae up to 2 mm thick).					+		158.64	158.67	0.03	C488158	3.60%	4600	2500														
																158.67	159.17	0.50	C488160	580.0	957	90.2	158.50	161.54	3.04	3.00	99	1.44	47	FR	MS	4	70	2	1	Cb
BD	85	158.67	170.69	12.02	SHL	OSR	LA	BK								159.17	159.67	0.50	C488161	152.5	666	40.4														
																159.67	160.17	0.50	C488162	103.5	272	26.6														
									Finely laminar, uniformly dark, black shale interbedded with uncommon grey limestone (silty vfg SS - GY SLT), which is finely laminar and rarely cross-bedded (low angle); v. rare calcite veinlets parallel to BD; common Sx (Py) lenses and bands up to 2 cm thick, parallel to BD, finely laminar and flat-bedded. The BK SHL is dominant over the whole interval, and is slightly darker and harder than the overlying BK SHLs above.							160.17	161.17	1.00	C488163	86.9	298	21.5	161.54	164.60	3.06	3.02	99	2.52	82	FR	MS	3	85	1	1	Cb
																161.17	162.17	1.00	C488164	114.0	314	37.0														
																162.17	163.17	1.00	C488165	129.5	290	38.1														
																163.17	164.67	1.50	C488166	132.5	243	39.2	164.60	167.64	3.04	3.07	101	1.97	65	FR	MS	4	85	1	1	Cb
																164.67	166.17	1.50	C488167	131.5	230	40.6														
																							167.64	170.69	3.05	2.46	81	2.13	70	FR	MS	1	80	1	1	Cb
																170.51	170.61	0.10	C488168	120.0	50	39.5														
									170.61 - 170.62 m Pyrite band about 1 cm thick							170.61	170.62	0.01	C488169	50.0	86	8.1														
		170.69							END OF HOLE							170.62	170.72	0.10	C488170	137.0	70	40.9														

NiMo PROJECT

PROPERTY: Rich

HOLE: RI07-08

Easting	Northing	Elev.	Depth (m)
444095	7357542		137.16

Contractor: North Star
Drill: MD-001

SURVEY							
Depth (m)	Azimuth	Dip	Method	Depth (m)	Azimuth	Dip	Method
collar	070°	-70°	compass				

Core size: BTW
Casing depth: 19.81 (m) out

Drilling dates: July 22 to 24, 2007

Logged by: D. MacDonald

Target: _____

SUMMARY				
From (m)	To (m)	Interval	Unit	Comments
0.00	18.24	18.24	OVB	
18.24	62.22	43.98	DME	
62.22	64.18	1.96	NiMo	
64.18	137.16	72.98	OSR	

SAMPLES	
Numbers:	C488201 - C488245
Total:	45
Date sent:	

COMMENTS

PROPERTY: RICH **HOLE:** RI07-08

Struct.		LITHOLOGY								ALT.			MINERALS				SAMPLES								Blocks			GEOTECHNICAL						JOINTS				
																												REC		RQD									
Type	Attitude	From (m)	To (m)	Interval (m)	Type	Unit	Texture	Modifier	Notes:				Ca	Sx	Fe		From (m)	To (m)	Interval (m)	Sample	Ni (ppm)	Zn (ppm)	Mo (ppm)	From (m)	To (m)	Intvl. (m)	(m)	Percent	(m)	Percent	Weathering	Hardness	Frequency	Attitude	Shape	Roughness	Infilling
		0.00	18.24	18.24	OB		FX	GY	Overburden - grey-black, highly fractured SHL fragments.	ex														0.00	12.19	12.19	0.45	4	0.00	0	MW	W					
																								12.19	15.24	3.05	0.13	4	0.00	0	MW	MS					
																								15.24	18.28	3.04	0.17	6	0.00	0	MW	MS					
BD	85	18.24	62.22	43.98	SHL	DME	LA	BK		m				+	+									18.28	21.35	3.07	0.53	17	0.00	0	MW	W					
									18.24 - 34.75 m Highly fractured and friable laminar black shale, highly weathered in top part of interval (to 27.60m); common limonite coating of abundant fracture surfaces; rare veinlets parallel to BD infilled with white, semi-fibrous mineral (no fizzing with HCl); uncommon Sx (Py) banding (2mm wide).													21.35	24.38	3.03	1.81	60	0.00	0	MW	VW					
																								24.38	27.43	3.05	1.75	57	0.00	0	HW	VW					
																								27.43	30.48	3.05	2.93	96	0.00	0	MW	VW					
																								30.48	33.53	3.05	2.92	96	0.00	0	MW	VW					
																								33.53	36.58	3.05	2.82	92	0.16	5	SW	VW	30	80	1	2	ALS
BD	80				SHL	DME	LA	BK		w				+	+									36.58	39.62	3.04	2.99	98	0.36	12	SW	MS	15	85	1	1	GYP
									34.75 - 51.89 m Finely laminar, flat-bedded BK SHL, interbedded with finely laminar, flat- to-slightly inclined bedded GY siliceous SLT, which SLT beds tend to become slightly more fine-grained with depth; GY SLT beds average ~5 - 7 cm thickness and generally have sharp contacts (over 3 - 5 mm), although some of the thinner beds have slightly gradational contacts (over 5 cm); uncommon-to-common Sx (Py) bands up to 5 mm thick; almost no Fe oxyhydroxides in this interval.																		39.62	42.67	3.05	3.06	100	0.14	5	SW	MS	15	85	2	1	ALS
																								42.67	45.72	3.05	2.80	92	0.67	22	SW	MS	15	85	1	3	GYP
																								45.72	48.77	3.05	3.10	102	0.20	7	SW	MS	10	85	2	1	ALS
																								48.77	51.82	3.05	3.05	100	0.00	0	SW	MS	10	10	2	3	ALS
BD	85				SHL	DME	LA	BK	51.89 - 62.22 m Flat-bedded, finely laminar BK SHL interbedded with uncommon GY SLT (finely laminar, fining upwards in general) beds up to 8 cm thick; BD angle shifts from 80 to 50 degrees in the last 4 m of the interval, then back to 70 degrees by the end of the interval. Common limonite + calcite on fracture surfaces in first 1 m of interval and again at 57.95 - 58.67 m; @ 58.67 to the end-of-interval, common calcite-filled veinlets ~parallel to BD about 3 - 4 mm wide.	f				+	+	+	54.62	56.12	1.50	C488201	137.0	826	39.2	51.82	54.87	3.05	1.70	56	0.00	0	SW	MS	15	85	1	1	Li
																	56.12	57.62	1.50	C488202	179.5	477	35.7														
																	57.62	58.62	1.00	C488203	163.5	299	35.3														
																	58.62	59.62	1.00	C488204	175.0	252	38.0	54.87	57.91	3.04	1.32	43	0.10	3	SW	MS	30	45	1	2	Li
																	59.62	60.62	1.00	C488205	201.0	207	60.3														
																	60.62	61.12	0.50	C488206	158.5	158	47.0														
																	61.12	61.62	0.50	C488207	246.0	229	70.6	57.91	60.93	3.02	2.57	85	0.30	10	MW	MS	25	60	1	3	Li

PROPERTY: RICH **HOLE:** RI07-08

Struct. Type	Struct. Attitude	LITHOLOGY From (m)	LITHOLOGY To (m)	LITHOLOGY Interval (m)	LITHOLOGY Type	LITHOLOGY Unit	LITHOLOGY Texture	LITHOLOGY Modifier	Notes:	ALT.			MINERALS Ca	MINERALS Sx	MINERALS Fe		SAMPLES From (m)	SAMPLES To (m)	SAMPLES Interval (m)	SAMPLES Sample	SAMPLES Ni (ppm)	SAMPLES Zn (ppm)	SAMPLES Mo (ppm)	Blocks From (m)	Blocks To (m)	Blocks Intvl. (m)	GEOTECHNICAL REC (m)	GEOTECHNICAL REC Percent	GEOTECHNICAL RQD (m)	GEOTECHNICAL RQD Percent	GEOTECHNICAL Weathering	GEOTECHNICAL Hardness	JOINTS Frequency	JOINTS Attitude	JOINTS Shape	JOINTS Roughness	JOINTS Infilling
																	61.62	61.92	0.30	C488208	184.0	437	36.0															
																	61.92	62.22	0.30	C488209	253.0	564	48.2															
																								60.93	64.01	3.08	2.97	96	1.54	50	SW	MS	8	60	1	1	ALS
BD	var	62.22	64.18	1.96	SX	NIMO	LA/I	BZ	62.22 - 63.93 m vfg, wavy, bronze sulfide laminae, highly distorted (slumped) and severely bioturbated, 'floating' in a BK SHL host; individual laminae vary highly in width (1 - 4 mm) and are up to 8 cm long; sulfides are not as concentrated as in typical NIMO horizons seen in other holes; interval comprises ~40 % NIMO + ~60 % BK SHL	w				+																												
BD	var				SX	NIMO	LA/I	BZ	63.93 - 64.18 m Slightly altered (tarnished) bronze, finely-to-moderately laminated sulfide bands that are moderately bioturbated and very wavy/distorted; several small 'rafts' (0.5 cm x 3 cm) have delaminated from the main body of concentrated sulfides and slumped into the underlying BK SHL. This interval of the NIMO Horizon is more concentrated in sulfides than the previous interval, and is more characteristic of NIMO seen in other holes.																															
BD	80	64.18	137.16	72.98	SHL	OSR	LA/I	BK		w				+			64.18	64.48	0.30	C488234	152	483	36.3	64.01	67.06	3.05	2.99	98	1.74	57	FR	MS	4	30	1	1	Cb
																	64.48	64.78	0.30	C488235	177.5	476	33.2															
																	64.78	65.28	0.50	C488236	88.8	256	26.8															
																	65.28	65.78	0.50	C488237	94.1	339	25.3															
									64.18 - 116.09 m Finely laminar, calcareous BK SHL, flatly bedded, interbedded with common GY silty LST fining upwards (LST beds up to 10 cm thick near top of interval, becoming thinner and less common with depth); BK SHL becomes slightly harder after about the first 2 m of the interval (slight recrystallization of carbonate); uncommon Sx (Py) bands 3 - 5 mm wide, parallel to BD								65.78	66.78	1.00	C488238	99.7	302	27.8	67.06	70.10	3.04	3.05	100	2.70	89	FR	MS	2	20	2	1	Cb
																	66.78	67.78	1.00	C488239	119.5	336	32.3															
																	67.78	68.78	1.00	C488240	130	244	35.6															
																	68.78	70.28	1.50	C488241	136.5	234	38.2	70.10	73.15	3.05											
																	70.28	71.78	1.50	C488242	132.5	209	36.6															
																								73.15	76.20	3.05	2.94	96	1.46	48	FR	MS	4	20	3	3	Cb
																	77.42	77.72	0.30	C488243	98.9	69	31.6	76.20	79.25	3.05	2.88	94	2.43	80	FR	MS	1	30	1	2	Cb
BD	85								bedding								77.72	77.73	0.01	C488244	87.2	25	19.2															
																	77.73	78.03	0.30	C488245	138.0	357	38.7															
																								79.25	82.30	3.05	3.09	101	2.19	72	FR	MS	2	30	1	1	Cb
																								82.30	85.34	3.04	3.02	99	2.73	90	FR	MS	2	30	2	2	Cb
																	NiMo SAMPLING				**%**	**%**															
																	62.22	62.22	0.01	C488210	1.14	0.68	766.0															
																	62.22	62.29	0.07	C488211	0.47	0.18	125.5	85.34	88.39	3.05	2.95	97	1.10	36	FR	MS	8	80	1	1	Cb
																	62.29	62.39	0.10	C488212	1.85	0.15	468.0															
																	62.39	62.50	0.11	C488213	2.10	0.14	550.0															
																	62.50	62.61	0.11	C488214	1.37	0.08	386.0	88.39	91.44	3.05	2.97	97	1.42	47	FR	MS	5	80	2	2	Cb
																	BLANK			C488215	0.01	<0.01	2.88															
																	62.61	62.71	0.10	C488216	1.72	0.08	472.0															
																	62.71	62.76	0.05	C488217	1.66	0.08	467.0	91.44	94.49	3.05	3.01	99	2.25	74	FR	MS	2	10	1	2	Cb
																	62.76	62.90	0.14	C488218	0.86	0.05	288.0															
																	62.90	63.03	0.13	C488219	0.25	0.02	118.5															
																	63.03	63.20	0.17	C488220	1.53	0.08	398.0	94.49	97.54	3.05	3.04	100	1.71	56	FR	MS	4	5	2	2	Cb
																	BLANK			C488221	0.01	<0.01	0.81															
																	63.20	63.31	0.11	C488222	1.37	0.07	434.0															
																	63.31	63.41	0.10	C488223	1.06	0.05	511.0	97.54	100.58	3.04	3.05	100	1.49	49	FR	MS	5	30	1	2	Cb
																	63.41	63.58	0.17	C488224	1.27	0.06	377.0															
																	63.58	63.74	0.16	C488225	1.03	0.05	324.0															
																	63.74	63.85	0.11	C488226	1.15	0.05	270.0	100.58	103.63	3.05	3.01	99	2.21	72	FR	MS	4	80	1	1	Cb
																	BLANK			C488227	0.01	<0.01	0.73															
																	63.85	63.95	0.10	C488228	0.73	0.04	187.5															
																	63.95	64.00	0.05	C488229	1.89	0.13	498.0	103.63	106.68	3.05	3.06	100	0.97	32	FR	MS	8	80	1	1	Cb

PROPERTY: RICH **HOLE:** RI07-08

Struct. Type	Struct. Attitude	LITHOLOGY From (m)	To (m)	Interval (m)	Type	Unit	Texture	Modifier	Notes:	ALT.	MINERALS Ca	Sx	Fe	SAMPLES From (m)	To (m)	Interval (m)	Sample	Ni (ppm)	Zn (ppm)	Mo (ppm)	Blocks From (m)	To (m)	Intvl. (m)	GEOTECHNICAL REC (m)	REC Percent	RQD (m)	RQD Percent	Weathering	Hardness	JOINTS Frequency	Attitude	Shape	Roughness	Infilling
														64.00	64.08	0.08	C488230	2.85	0.25	713.0														
														64.08	64.11	0.03	C488231	1.89	0.99	1055.0														
														64.11	64.18	0.07	C488232	1.12	0.25	501.0	106.68	109.73	3.05	3.00	98	0.95	31	FR	MS	7	80	1	1	Cb
														BLANK			C488233	0.01	<0.01	1.54														
																					109.73	112.78	3.05	3.00	98	1.50	49	FR	MS	3	30	1	1	Cb
																					112.78	115.83	3.05	3.06	100	1.53	50	FR	MS	3	80	1	1	Cb
																					115.83	118.87	3.04	3.09	102	1.32	43	FR	MS	2	10	1	1	Cb
BD	80				LST	OSR	LA/I	GY	116.09 - 121.87 m Interval starts with finely laminar BK SHL interbedded with fg GY calcareous SLT/LST; BK SHL beds are 10 - 15 cm thick, LST beds are 2 mm - 5 cm thick, until about the 119 m mark, where the silty LST becomes dominant over the remainder of the interval; at 119 m, GY silty LST is finely interbedded with calcareous BK SHL beds up to 5 cm thick (avg 2 cm); grainsize in the GY LST varies unpredictably from silt to m-cg sandstone, and most beds have sharp, distorted contacts and are internally varied from flat-bedded to lensoid to wavy laminar; common soft-sediment deformation and erosional features (rip-up clasts, scours); some beds show X-stratification and fine downwards, whereas others are flat-bedded and fine upwards, with bioturbation. N.B. Intervals [(64.18 - 116.09 m) + (116.09 - 121.87 m)] and [(121.87 - 130.60 m) + (130.60 - 137.16 m)] comprise 2 'cycles' of (BK SHL + LST).	w			+																											
																					118.87	121.92	3.05	3.05	100	2.35	77	FR	MS	3	60	1	2	Cb
BD	80				SHL	OSR	LA	BK	121.87 - 130.06 m Same lithology and characteristics as BK SHL in interval 64.18 - 116.09 m	w			+	+						121.92	124.97	3.05	3.09	101	0.71	23	FR	MS	4	20	3	3	Cb
																					124.97	128.17	3.20	3.08	96	0.72	23	FR	MS	5	10	3	2	Cb
																					128.01	131.06	3.05	2.98	98	2.17	71	FR	MS	2	20	2	2	Cb
BD	70 - 85				LST	OSR	LA/I	GY	130.60 - 137.16 m EOH Same lithology as interval 116.09 - 121.87 m, except that LSTs exhibit a more uniform grainsize distribution (I.e., more uniformly silty with rare cg sandstones), and exhibits less abundant erosional features.	w			+																									
																					131.06	134.11	3.05	3.11	102	2.58	85	FR	MS	1	60	2	1	Cb
		137.16							END OF HOLE												134.11	137.16	3.05	3.06	100	2.45	80	FR	MS	2	60	1	2	Cb

NiMo PROJECT

PROPERTY: Rich

HOLE: RI07-10

Easting	Northing	Elev.	Depth (m)
444095	7357542		82.30

Contractor: North Star
Drill: MD-001

SURVEY							
Depth (m)	Azimuth	Dip	Method	Depth (m)	Azimuth	Dip	Method
collar	070°	-75°	compass				

Core size: BTW
Casing depth: 19.81 (m) in*

Drilling dates: July 25 to 26, 2007

Logged by: D. MacDonald

Target: Same pad as RI07-08, targeting large NiMo intersection at a steeper angle

SUMMARY				
From (m)	To (m)	Interval	Unit	Comments
0	9.14	9.14	OVB	
9.14	65.82	56.68	DME	
65.82	65.88	0.06	NiMo	
65.88	82.3	16.42	OSR	

SAMPLES	
Numbers:	C488246 - C488263
Total:	18
Date sent:	August 12, 2007

COMMENTS

*lost 4' of casing down hole

PROPERTY: RICH **HOLE:** RI07-10

Struct.		LITHOLOGY								ALT.	MINERALS			SAMPLES							Blocks			GEOTECHNICAL						JOINTS				
																								REC		RQD									
Type	Attitude	From (m)	To (m)	Interval (m)	Type	Unit	Texture	Modifier	Notes:		Ca	Sx	Fe	From (m)	To (m)	Interval (m)	Sample	Ni (ppm)	Zn (ppm)	Mo (ppm)	From (m)	To (m)	Intvl. (m)	(m)	Percent	(m)	Percent	Weathering	Hardness	Frequency	Attitude	Shape	Roughness	Infilling
		0.00	9.14	9.14	OVB				0 - 9.14 m Overburden																									
BD	80	9.14	65.82	56.68	SHL	DME	LA	BK		m	+		+								9.14	12.19	3.05	0.50	16	0.00	0	MW	VW	30	70	2	2	
									9.14 - 36.01 m Alternating beds of finely laminar, flat-bedded, highly fissile and friable, earthy and weathered BK SHL and finely laminar GY-BK SHL that is fissile and less weathered and less friable; earthy BK SHL beds average 2 m in thickness; GY-BK harder SHL average bed thickness is 15 - 30 cm; rare beds of thinly laminar GY LST near middle and end of interval; common limonite +/- hematite coatings on abundant fracture surfaces.													12.19	15.24	3.05	0.12	4	0.00	0	MW	MS	30	M	3	2	
																					15.24	18.28	3.04	0.08	3	0.00	0	MW	W	30	M	3	2	
																					18.28	21.35	3.07	0.10	3	0.00	0	EW	VW	30				
																					21.35	24.38	3.03	1.50	50	0.00	0	HW	VW	30	70	2	2	
																					24.38	27.43	3.05	0.75	25	0.00	0	HW	VW	30	70	2	2	Li
																					27.43	30.48	3.05	2.53	83	0.00	0	MW	W	30	70	2	2	Li
																					30.48	33.53	3.05	2.85	93	0.32	10	SW	VW	30	70	2	2	Li
																					33.53	36.58	3.05	2.63	86	0.10	3	SW	VW	30	70	2	2	Li
BD	70				SHL	DME	LA	BK		w	+	+	+								36.58	39.62	3.04	2.85	94	0.11	4	FR	MS	30	70	2	2	Li
									36.01 - 61.00 m Finely laminar, moderately fissile BK SHL interbedded with rare, calcareous, fg - mg silt/sandy silt beds (up to 30 cm thick) and also interbedded with abundant siliceous GY SLT/fg SS. Both BK SHL, calcareous GY SLT and siliceous GY SLT exhibit general fining downward trends within beds, and the whole interval fines downward also; common calcite veinlets parallel to bedding; competence increases with depth; uncommon Sx (Py) laminae parallel to BD up to 2 - 3 mm thick; uncommon limonite on fracture surfaces near top of interval																39.62	42.67	3.05	2.70	89	0.23	8	FR	MS	30	70	2	2	GYP
																					42.67	45.72	3.05	2.97	97	0.20	7	FR	MS	20	70	2	2	GYP
																					45.72	48.77	3.05	2.97	97	0.82	27	FR	MS	20	70	1	1	GYP
																					48.77	51.82	3.05	3.05	100	0.39	13	FR	MS	20	70	1	1	GYP
																					51.82	54.87	3.05	2.96	97	0.00	0	FR	MS	30	70	1	1	GYP
																					54.87	57.91	3.04	2.92	96	0.00	0	FR	MS	30	70	1	1	Cb
														58.32	59.82	1.50	C488246	166.5	665	46.4	57.91	60.93	3.02	2.70	89	0.00	0	FR	MS	30	70	1	1	GYP
														59.82	61.32	1.50	C488247	133.5	239	40.5														
														61.32	62.32	1.00	C488248	161	201	40.4														
BD	75				SHL	DME	LA	BK	61.00 - 65.82 m Finely laminar, fissile BK SHL continued, but moderately fractured in mostly random orientations; common infilling of veinlets (1 mm - 5 mm wide) by calcite + white, semi-fibrous, crystalline mineral; interva is moderately physically weathered, and is earthy to touch and smell.	f	+	+			62.32	63.32	1.00	C488249	182.5	226	51.1	60.93	64.01	3.08	2.62	85	0.10	3	FR	MS	30	80	1	1	GYP
														63.32	64.32	1.00	C488250	303	457	54.8														
														64.32	64.82	0.50	C488251	186	201	57.9														
														64.82	65.32	0.50	C488252	208	246	62.6	64.01	67.06	3.05	2.90	95	0.66	22	FR	MS	15	70	1	1	Cb
														65.32	65.82	0.50	C488253	549	493	43.3														

PROPERTY: RICH **HOLE:** RI07-10

Struct.		LITHOLOGY								ALT.			MINERALS				SAMPLES							Blocks			GEOTECHNICAL						JOINTS				
																											REC		RQD									
Type	Attitude	From (m)	To (m)	Interval (m)	Type	Unit	Texture	Modifier	Notes:				Ca	Sx	Fe		From (m)	To (m)	Interval (m)	Sample	Ni (ppm)	Zn (ppm)	Mo (ppm)	From (m)	To (m)	Intvl. (m)	(m)	Percent	(m)	Percent	Weathering	Hardness	Frequency	Attitude	Shape	Roughness	Infilling
BD	60	65.82	65.88	0.06	SX	NIMO	LA/E	BZ	65.82 - 65.88 m NIMO Horizon - vfg bronze Sx laminae that are moderately bioturbated and slumped/distorted, with small amounts of calcite (v. slight fizzing with HCl)	w			+	+			65.82	65.88	0.06	C488254	2.64%	0.59%	0.14%														
BD	80	65.88	82.30	16.42	SHL	OSR	LA	BK	65.88 - 82.30 m Wavy-to-flat finely laminar, calcareous BK SHL (dominant in interval) (v. competent + harder than overlying SHLs, partially recrystallized carbonate, increased organic content relative to overlying SHLs) interbedded with finely laminar, mostly flat-bedded, fg silty GY LST (~80% SHL, ~20% LST in interval); GY LST beds generally fining upwards and becoming thinner with depth (range 1mm - 70 cm, avg 3 - 5 cm thick); one v thick LST bed @ 67.11 - 67.81 m, exhibits coarsening upwards trend (N.B. Fizzing with HCl starts at about 66.83 m, i.e., BK SHL becomes calcareous, not corresponding to any visible change in lithology, structure or texture; uncommon Sx lenses and bands up to 3 - 4 mm thick) EOH	w			+	+			65.88	66.38	0.50	C488256	347	712	83.8														
																	66.38	66.88	0.50	C488257	134	305	30.8	67.06	70.10	3.04	2.95	97	2.14	70	FR	MS	3	70	1	1	Cb
																	66.88	67.38	0.50	C488258	62.3	156	19.1														
																	67.38	68.38	1.00	C488259	67.9	239	19.55														
																	68.38	69.38	1.00	C488260	109	417	31.1	70.10	73.15	3.05	2.83	93	2.50	82	FR	MS	2	70	1	1	Cb
																	69.38	70.38	1.00	C488261	112	373	31.6														
																	70.38	71.88	1.50	C488262	135	323	38.4														
																	71.88	73.38	1.50	C488263	143	314	40.9	73.15	76.20	3.05	3.09	101	2.30	75	FR	MS	3	70	1	1	Cb
																	BLANK			C488255	4	16	0.31														
																								76.20	79.25	3.05	3.03	99	2.33	76	FR	MS	2	70	1	1	Cb
		82.30							END OF HOLE															79.25	82.30	3.05	3.04	100	2.62	86	FR	MS	2	70	1	1	Cb

NiMo PROJECT

PROPERTY: Rich

HOLE: RI07-12

Easting	Northing	Elev.	Depth (m)
443936	7357825		94.49

Contractor: North Star
Drill: MD-002

SURVEY							
Depth (m)	Azimuth	Dip	Method	Depth (m)	Azimuth	Dip	Method
collar	070°	-60°	compass				

Core size: BTW
Casing depth: 15.24 (m) out

Drilling dates: July 27 to 30, 2007

Logged by: D. MacDonald

Target: _____

SUMMARY				
From (m)	To (m)	Interval	Unit	Comments
0.00	15.24	15.24	OVB	
15.24	83.12	67.88	DME	
83.12	83.17	0.05	NiMo	
83.17	94.49	11.32	OSR	

SAMPLES	
Numbers:	C488264 - C488286
	C488292 - C488293
Total:	23
Date sent:	August 12, 2007

COMMENTS

Additional sulphide layer identified during splitting, two samples inserted into sequence.

PROPERTY: RICH **HOLE:** RI07-12

Struct.		LITHOLOGY								ALT.			MINERALS				SAMPLES							Blocks			GEOTECHNICAL						JOINTS				
																											REC		RQD									
Type	Attitude	From (m)	To (m)	Interval (m)	Type	Unit	Texture	Modifier	Notes:				Ca	Sx	Fe		From (m)	To (m)	Interval (m)	Sample	Ni (ppm)	Zn (ppm)	Mo (ppm)	From (m)	To (m)	Intvl. (m)	(m)	Percent	(m)	Percent	Weathering	Hardness	Frequency	Attitude	Shape	Roughness	Infilling
		0.00	15.24	15.24	OVB				0 - 15.24 m Overburden																												
BD	75-8	15.24	83.12	67.88	SHL	DME	LA	BK		w			+	+										15.24	18.28	3.04	1.91	63	0.00	0	MW	VW	30	85	2	2	Li
									15.24 - 44.68 Interval starts with highly fissile and slightly friable laminar BK SHL, interbedded with abundant, GY siliceous SLT (gradationally and sharply contacts with the BK SHL) ranging in thickness from 1 cm - 25 cm, and with rare, GY calcareous SLT (slightly sandy) - comprises first of 6 coarsening downwards cycles in the DME of BK SHL grading into GY sandy SLT by end of interval; transition in grainsize is gradual, over ~5 m. Rare Sx (Py) flecks; common veinlets mostly parallel to BD up to 1 cm wide and filled with quartz. Almost no veinlets occur below this first interval.																	18.28	21.35	3.07	2.95	96	0.00	0	SW	MS	30	85	2	2	GYP
																								21.35	24.38	3.03	2.87	95	0.00	0	SW	MS	25	80	2	2	GYP
																								24.38	27.43	3.05	3.00	98	0.00	0	FR	MS	25	80	2	2	GYP
																								27.43	30.48	3.05	2.80	92	0.12	4	FR	MS	20	70	2	2	GYP
																								30.48	33.53	3.05	2.85	93	0.00	0	FR	MS	20	70	2	2	Cb
																								33.53	36.58	3.05	3.00	98	0.00	0	FR	MS	20	70	2	2	Cb
																								36.58	39.62	3.04	2.39	79	0.00	0	FR	MS	20	70	2	2	Cb
																								39.62	42.67	3.05	1.45	48	0.00	0	FR	MS	25	70	2	2	Cb
																								42.67	45.72	3.05	2.76	90	0.00	0	FR	MS	20	80	2	2	Cb
BD	80				SHL	DME	LA	BK		w			+																								
									44.68 - 49.58 m 2nd coarsening downward cycle; Mostly finely laminar BK SHL interbedded with abundant GY siliceous SLT-fg SS (up to ~20 cm thick with gradational, subtle upper boundaries) + rare GY calcareous GY SLT.													45.72	48.77	3.05	2.98	98	1.05	34	FR	MS	8	80	2	2	Cb
																								48.77	51.82	3.05	3.07	101	0.75	25	FR	MS	10	80	2	2	ALS

PROPERTY: RICH **HOLE:** RI07-12

Struct. Type	Struct. Attitude	LITHOLOGY From (m)	To (m)	Interval (m)	Type	Unit	Texture	Modifier	Notes:	ALT.	MINERALS Ca	Sx	Fe	SAMPLES From (m)	To (m)	Interval (m)	Sample	Ni (ppm)	Zn (ppm)	Mo (ppm)	Blocks From (m)	To (m)	Intvl. (m)	GEOTECHNICAL REC (m)	REC Percent	RQD (m)	RQD Percent	Weathering	Hardness	JOINTS Frequency	Attitude	Shape	Roughness	Infilling
BD	80-75				SHL	DME	LA	BK-	49.58 - 54.59 m 3rd coarsening downward cycle (BK SHL to GY sandy SLT); Finely laminar BK-GY SHL interbedded with GY siliceous SLT (up to 30 cm thick, graded beds with gradational upper contacts) and rare, calcareous GY SLT beds up to 8 cm thick; rare, disseminated vfg flakes of Py in last 2 m of interval.	w	+	+																												
																					51.82	54.87	3.05	3.02	99	1.28	42	FR	MS	10	80	2	2	ALS
BD	80				SHL	DME	LA	BK-	54.59 - 57.75 m 4th coarsening downward cycle (BK-GY SHL to GY fg-mg SS); finely laminar BK SHL interbedded with common GY siliceous SLT to sandy SLT beds ~8 cm thick; rare calcareous GY SLT beds with rare X-stratification; sharp, erosional lower contact	w	+																													
																					54.87	57.91	3.04	3.06	101	1.04	34	FR	MS	11	80	2	2	ALS
BD	80				SHL	DME	LA	BK-	cycle; Sharp upper contact (erosional scour) into finely laminar BK SHL interbedded with abundant GY siliceous SLT beds up to several cm thick, and with v rare laminar GY silty LST; interval ends in mg-cg siliceous SS.	w	+																													
																					57.91	60.93	3.02	3.04	101	0.56	19	FR	MS	18	80	2	2	ALS
																					60.93	64.01	3.08	3.09	100	0.56	18	FR	MS	18	80	2	2	ALS
																					64.01	67.06	3.05	3.07	101	1.35	44	FR	MS	9	80	2	2	ALS
BD	85				SHL	DME	LA	BK	65.24 - 69.09 m 6th coarsening downward cycle; Moderately finely laminar, flat-bedded BK SHL interbedded with GY siliceous SLT (almost fg silty SS) beds up to 20 cm thick; rare Sx (Py) bands (1 - 2 mm thick); grainsize increases to fg SS at end of interval; sharp upper contact.	w		+																												
																					67.06	70.10	3.04	3.06	101	1.39	46	FR	MS	10	80	2	2	ALS
BD	85				SHL	DME	LA	BK	69.09 - 83.12 m 7th coarsening downward cycle; interval starts with finely laminar BK SHL interbedded with GY silty LST beds (uncommon, up to 20 cm thick; uncommon Py lenses parallel to bedding (3mm x 2 cm); almost no veinlets in this interval; gradational lower and upper contacts (`5 cm)	w	+	+		82.72	82.74	0.02	C488292	3.04%	0.32%	1270																				
														82.74	83.12	0.38	C488293	3900	1030	264	70.10	73.15	3.05	2.93	96	1.75	57	FR	MS	7	80	2	2	ALS
																					73.15	76.20	3.05	3.00	98	1.17	38	FR	MS	9	80	2	2	ALS
														72.25	73.75	1.50	C488264	123.0	1010	39.7														
														73.75	75.25	1.50	C488265	117.5	529	43.9														
														75.25	76.25	1.00	C488266	164.5	698	44.5	76.20	79.25	3.05	2.60	85	0.50	16	FR	MS	20	80	2	2	ALS
														76.25	77.25	1.00	C488267	169.5	309	46.1														
														77.25	78.25	1.00	C488268	132.0	218	37.9														
														78.25	78.75	0.50	C488269	96.5	146	32.4	79.25	82.30	3.05	0.28	9	0.00	0	FR	MS	20	80	2	2	ALS
														78.75	79.25	0.50	C488270	137.5	171	46.1														
									79.25 TO 82.60 poor recovery (30 cm)					79.25	82.60	3.35	C488271	133.0	347	36.9														

PROPERTY: RICH **HOLE:** RI07-12

Struct.		LITHOLOGY								ALT.			MINERALS			SAMPLES							Blocks			GEOTECHNICAL						JOINTS					
																										REC		RQD									
Type	Attitude	From (m)	To (m)	Interval (m)	Type	Unit	Texture	Modifier	Notes:				Ca	Sx	Fe	From (m)	To (m)	Interval (m)	Sample	Ni (ppm)	Zn (ppm)	Mo (ppm)	From (m)	To (m)	Intvl. (m)	(m)	Percent	(m)	Percent	Weathering	Hardness	Frequency	Attitude	Shape	Roughness	Infilling	
									82.97 BK SHL becomes abruptly softer until 83.47 m mark, after which depth the BK SHL becomes harder than overlying SHLs.							82.60	83.12	0.52	C488272	179.0	683	41.8	82.30	85.34	3.04	2.72	89	1.05	35	FR	MS	15	80	2	2	Cb	
BD	var	83.12	83.17	0.05	SX	NIMO	LA/I	BZ	83.12 - 83.17 m Finely laminar, mildly bioturbated bronze Sx bands up to 0.8 cm thick; some delamination of laminae which form floating rafts in underlying BK SHL	w				+		83.12	83.17	0.05	C488273	1.78%	0.98%	930															
BD	85	83.17	94.99	11.82	SHL	OSR	LA	BK	83.17 - 83.89 m Finely laminar, flat-bedded BK SHL that becomes slightly harder and darker, as well as becoming calcareous at the 83.47 m mark. Rare Py laminae up to 2 mm thick.	w			+	+		83.17	83.47	0.30	C488274	395.0	946	83.5															
BA					BAL	OSR	BA/I	GY	83.89 - 84.41 m GY, slightly brecciated LST BALL; fizzes intensely with HCl; internally brecciated, and veinlets are common (fragments 3 cm x 3 cm; calcite matrix ~1 cm wide at maximum point)	w			+			83.47	83.89	0.42	C488275	62.3	205	19.3	85.34	88.39	3.05	2.91	95	1.44	47	FR	MS	3	80	2	2	Cb	
BD	85-90				SHL	OSR	LA	BK		w			+	+		83.89	84.41	0.52	C488277	24.5	73	7.08															
																84.41	84.91	0.50	C488278	113.5	224	31.6															
									84.41 - 84.99 m (EOH) BK SHL ctd. Finely laminar, almost massive, flat-bedded, dark BK SHL that is calcareous from 84.50 m to EOH, and has recrystallization textures on fresh fracture surfaces; almost free of veinlets and natural fractures; common Sx (Py) bands and lenses (up to 1 cm diam/width); BK SHL in this interval is harder than that between the NIMO and LST BALL, and harder than the DME SHLs above.							84.91	85.91	1.00	C488279	121.5	365	32.5	88.39	91.44	3.05	3.00	98	2.27	74	FR	MS	3	80	2	2	Cb	
																85.91	86.91	1.00	C488280	101.0	290	28.3															
																86.91	87.91	1.00	C488281	126.0	294	35.3															
																87.91	89.41	1.50	C488282	129.5	196	36.8	91.44	94.49	3.05	3.12	102	2.39	78	FR	MS	3	80	2	2	Cb	
																89.41	90.91	1.50	C488283	127.0	176	38.2															
																93.85	94.15	0.30	C488284	123.5	371	50.3															
																94.15	94.16	0.01	C488285	157.0	974	34.4															
																94.16	94.46	0.30	C488286	152.0	119	51.2															
		94.49							END OF HOLE							BLANK			C488276	3.5	21	0.57															

NiMo PROJECT

PROPERTY: Rich

HOLE: RI07-13

Easting	Northing	Elev.	Depth (m)
443753	7358014		103.63

Contractor: North Star
Drill: MD-002

SURVEY							
Depth (m)	Azimuth	Dip	Method	Depth (m)	Azimuth	Dip	Method
collar	060°	-60°	compass				

Core size: BTW
Casing depth: 44.20 (m) out

Drilling dates: July 28 to 29, 2007

Logged by: D. MacDonald

Target: _____

SUMMARY				
From (m)	To (m)	Interval	Unit	Comments
0.00	41.00	41.00	OVB	
41.00	103.63	62.63	DME	

SAMPLES

Numbers: C488287 - C488291

Total: 5
Date sent: August 16, 2007

COMMENTS

Hole stopped short.

PROPERTY: RICH **HOLE:** RI07-13

Struct.		LITHOLOGY								ALT.			MINERALS				SAMPLES							Blocks			GEOTECHNICAL						JOINTS				
																											REC		RQD									
Type	Attitude	From (m)	To (m)	Interval (m)	Type	Unit	Texture	Modifier	Notes:				Ca	Sx	Fe		From (m)	To (m)	Interval (m)	Sample	Ni (ppm)	Zn (ppm)	Mo (ppm)	From (m)	To (m)	Intvl. (m)	(m)	Percent	(m)	Percent	Weathering	Hardness	Frequency	Attitude	Shape	Roughness	Infilling
		0.00	41.00	41.00	OVB				0 - 41 m Extremely weathered, (what once might have been black shale) black mud and sand, v clayey; too weathered to discern structures, textures or detailed mineralogy	ex																												
BD	85	41.00	103.63	62.63	SHL	DME	LA	BK	41 - 49.36 m Moderately fissile, finely laminar BK SHL that increases in grainsize slightly in last 1 m of interval; BK SHL has rare thin beds of siliceous GY SLT near bottom of interval (up to 2 cm thick, finely laminar); degree of weathering decreases with depth, and core is v competent by the 43.30 m mark.	f-w															39.62	42.67	3.05	0.70	23	0.00	0	MW	VW	30	90				
																								42.67	45.72	3.05	1.75	57	0.00	0	SW	W	15	85	2	2	GYP
																								45.72	48.77	3.05	2.98	98	0.10	3	SW	MS	15	85	2	2	GYP
																	48.76	49.06	0.30	C488287	161.5	239	65.1														
																	49.06	49.36	0.30	C488288	137.5	225	58.1	48.77	51.82	3.05	2.83	93	0.00	0	SW	MS	15	85	2	2	GYP
BD	80				SHL	DME	LA	BK	49.36 - 49.80 m Finely laminar BK SHL with abundant Sx (Py) bands, lenses and beds; Py beds are 2 - 5 cm thick, and some beds are more concentrated in Py than others, almost to the point that some have a disseminated appearance	w				+			49.36	49.80	0.44	C488289	490.0	2590	69.9															
BD	60-80				SHL	DME	LA	BK		w			+	+			49.80	50.10	0.30	C488290	241.0	699	81.7														
																	50.10	50.40	0.30	C488291	121.5	264	51.0	51.82	54.87	3.05	2.77	91	0.00	0	FR	MS	15	60	2	2	GYP
									49.80 - 71.00 m Finely laminated, flat-to-inclined bedded BK SHL with GY overtones, interbedded with rare-to-uncommon calcareous (2 cm width common, to 50 cm width rare) and non-calcareous GY SLT beds (up to 3 cm thick); grainsize of both the BK-GY SHL and GY SLT increases slightly in general, over the whole interval (ending n silty BK-GY SHL); last 3 - 4 m of interval are strongly veined (1 mm diam calcite) and slightly brecciated (angular GY-BK SHL fragments up to 3 cm x 2 cm in calcite matrix); uncommon Sx (Py) laminae up to 2 mm wide)															54.87	57.91	3.04	2.38	78	0.00	0	FR	MS	15	60	2	2	Cb
																								57.91	60.93	3.02	2.95	98	0.40	13	FR	MS	15	60	2	2	Cb
																								60.93	64.01	3.08	3.10	101	0.13	4	FR	MS	15	60	2	2	Cb
																								64.01	67.06	3.05	2.84	93	0.13	4	FR	MS	15	40	2	2	Cb

PROPERTY: RICH **HOLE:** RI07-13

Struct.		LITHOLOGY								ALT.			MINERALS				SAMPLES							Blocks			GEOTECHNICAL						JOINTS				
																											REC		RQD									
Type	Attitude	From (m)	To (m)	Interval (m)	Type	Unit	Texture	Modifier	Notes:				Ca	Sx	Fe		From (m)	To (m)	Interval (m)	Sample	Ni (ppm)	Zn (ppm)	Mo (ppm)	From (m)	To (m)	Intvl. (m)	(m)	Percent	(m)	Percent	Weathering	Hardness	Frequency	Attitude	Shape	Roughness	Infilling
																								67.06	70.10	3.04	1.95	64	0.00	0	FR	MS	20	40	2	2	Cb
																								70.10	73.15	3.05	2.00	66	0.00	0	FR	MS	20	85	2	2	Cb
BD	80				SHL	DME	LA	BK-		w			+	+																							
																								73.15	76.20	3.05	2.98	98	0.00	0	FR	MS	15	85	2	2	GYP
									71.00 - 88.29 m Brecciation of previous interval stops abruptly (< 1 cm); laminar BK-GY SHL interbedded with common, mostly non-calcareous, finely-to-moderately laminar GY SLT beds that exhibit rare X-stratification (low-angle); also, in last 3 - 4 m of interval are rare, v finely laminar, calcareous GY SLT (almost sandy) beds (8 - 15 cm thick) that fine upwards generally, and have fairly sharp (~3 mm) upper and lower boundaries; uncommon Sx (Py) lenses/blebs up to 0.5 cm thick																		76.20	79.25	3.05	3.03	99	0.67	22	FR	MS	15	85	2	2	GYP
																								79.25	82.30	3.05	2.87	94	1.22	40	FR	MS	10	85	2	2	GYP
																								82.30	85.34	3.04	3.15	104	0.63	21	FR	MS	10	85	2	2	GYP
																								85.34	88.39	3.05	2.98	98	1.35	44	FR	MS	8	85	2	2	GYP
BD	80-85				SHL	DME	LA	BK		w			+																							
																								88.39	91.44	3.05	3.08	101	1.71	56	FR	MS	8	80	2	2	GYP
									88.29 - 103.63 m (EOH) v finely laminar, flat-bedded BK SHL (darker than overlying BK-GY SHLs of previous intervals) interbedded with rare, finely-to-crudely laminar beds of GY calcareous SLT/LST up to 2 cm thick (mostly fining upwards); slight decrease in grainsize o BK SHL across the whole interval													91.44	94.49	3.05	3.07	101	0.81	27	FR	MS	8	80	2	2	GYP
																								94.49	97.54	3.05	3.02	99	1.80	59	FR	MS	5	80	2	2	GYP
																								97.54	100.58	3.04	2.95	97	1.48	49	FR	MS	6	80	2	2	GYP
		103.63							END OF HOLE															100.58	103.63	3.05	2.80	92	0.75	25	FR	MS	11	80	2	2	GYP

NiMo PROJECT

PROPERTY: Rich

HOLE: RI07-14

Easting	Northing	Elev.	Depth (m)
444130	7357445		60.96

Contractor: North Star
Drill: MD-001

SURVEY							
Depth (m)	Azimuth	Dip	Method	Depth (m)	Azimuth	Dip	Method
collar	070°	-80°	compass				

Core size: BTW
Casing depth: 21.33 (m) out

Drilling dates: July 30 to August 2, 2007

Logged by: D. MacDonald

Target: _____

SUMMARY				
From (m)	To (m)	Interval	Unit	Comments
0.00	43.30	43.30	OVB	
43.30	60.96	17.66	DME	

SAMPLES

Numbers:

Total: 0
Date sent:

COMMENTS

Hole collapsed, abandoned and retried

PROPERTY: RICH **HOLE:** RI07-14

Struct.		LITHOLOGY								ALT.			MINERALS				SAMPLES							Blocks			GEOTECHNICAL						JOINTS				
																											REC		RQD									
Type	Attitude	From (m)	To (m)	Interval (m)	Type	Unit	Texture	Modifier	Notes:								From (m)	To (m)	Interval (m)	Sample				From (m)	To (m)	Intvl. (m)	(m)	Percent	(m)	Percent	Weathering	Hardness	Frequency	Attitude	Shape	Roughness	Infilling
		0.00	43.30	43.30	OVB				Overburden, high clay content																												
																								42.67	45.72	3.05	1.30	43	0.00	0	SW	VW	20	50	1	1	ALS
BD	70	43.40	60.96	17.56	SHL	DME	LA	BK																45.72	48.77	3.05	1.65	54	0.00	0	FR	W	15	50	1	1	ALS
									43.30 - 60.69 m Finely laminar BK SHL, highly fractured in first 4 m; slightly inclined bedding; rare, high-angle calcite veinlets in first 3 m of interval, ~3mm wide, mostly perpendicular to BD; small zones of sedimentary breccia (up to 10 cm wide), semi-rounded to subangular BK-GY SHL clasts, average 5 mm x 5 mm, matrix-supported - matrix is light GY SLT; interval fines downward in general; BK SHL interbedded with GY SLT to GY laminar fg-mg SS with rare X-stratification; core becomes darker over last ~6m of interval, and slightly softer in last 50 cm of hole. EOH											48.77	51.82	3.05	2.80	92	0.00	0	FR	MS	20	50	1	1	ALS
																								51.82	54.87	3.05	3.18	104	0.00	0	FR	MS	30	60	1	1	ALS
																								54.87	57.91	3.04	2.67	88	0.00	0	FR	MS	10	60	1	1	ALS
																								57.91	60.96	3.05	2.28	75	0.00	0	FR	MS	20	60	1	1	ALS
		60.96							END OF HOLE																												

NiMo PROJECT

PROPERTY: Rich

HOLE: RI07-14A

Easting	Northing	Elev.	Depth (m)
444130	7357445		82.30

Contractor: North Star
Drill: MD-001

SURVEY							
Depth (m)	Azimuth	Dip	Method	Depth (m)	Azimuth	Dip	Method
collar	070°	-50°	compass				

Core size: BTW
Casing depth: 38.10 (m) out

Drilling dates: August 3 to 4, 2007

Logged by: D. MacDonald

Target: _____

SUMMARY				
From (m)	To (m)	Interval	Unit	Comments
0.00	41.34	41.34	OVB	
41.34	64.61	23.27	DME	
64.61	64.94	0.33	NiMo	very poor recovery, no NiMo seen
82.30	82.30	0.00	OSR	

SAMPLES

Numbers:

Total: 20
Date sent:

COMMENTS

Discrepency between drillers reported EOH (280') and last block in box (270')

PROPERTY: RICH **HOLE:** RI07-14A

Struct. Type	Struct. Attitude	LITHOLOGY From (m)	To (m)	Interval (m)	Type	Unit	Texture	Modifier	Notes:	ALT.			MINERALS Ca	Sx	Fe	Ba	SAMPLES From (m)	To (m)	Interval (m)	Sample	Ni (ppm)	Zn (ppm)	Mo (ppm)	Blocks From (m)	To (m)	Intvl. (m)	GEOTECHNICAL REC (m)	REC Percent	RQD (m)	RQD Percent	Weathering	Hardness	JOINTS Frequency	Attitude	Shape	Roughness	Infilling
		0.00	41.34	41.34	OVB				clay and black sand																												
BD	80	41.34	64.61	23.27	SHL	DME	LA	BK-	41.34 - 54.25 m Moderately fissile, laminar, BK GY SHL, mostly flat-bedded, interbedded with common-to-abundant, finely laminar GY slightly sandy SLT with subtle, gradational contacts, mostly conformable to SHL beds; almost no veinlets in the interval; common fractured, with surfaces commonly coated with limonite; v. rare, thin (1 - 5 cm) beds of calcareous, finely laminar GY SLT; uncommon, thin (0.5 cm) Sx (Py) bands that are v finely laminar; BK SHL becomes slightly more competent with depth, except for last 2 m of interval, where it becomes more fissile.	w-f			+	+	+																														
																									41.34	42.67	1.33	1.32	99	0.00	0	MW	VW	30	80	2	2	Li
																									42.67	45.72	3.05	2.45	80	0.00	0	SW	VW	30	80	2	2	Li
																									45.72	48.77	3.05	2.38	78	0.00	0	FR	MS	30	80	2	2	Li
																									48.77	51.82	3.05	2.94	96	0.00	0	FR	MS	15	80	2	2	Li
																									51.82	54.87	3.05	2.65	87	0.00	0	FR	MS	30	80	2	2	ALS
BD	80				SHL	DME	Bx	BK-		w			+																									
									54.25 - 60.12 m Same BK SHL as in previous interval, except highly fractured (brecciated) and broken up to pebble-cobble sized pieces; rare, high-angle calcite veinlets up to 1 cm apparent thickness.								55.12	56.62	1.50	C488371	144.5	993	29.9	54.87	57.91	3.04	1.15	38	0.00	0	FR	MS	30	80	2	2	Qz
																	56.62	58.12	1.50	C488372	276.0	521	38.4														
																	58.12	59.12	1.00	C488373	161.5	689	26.5														
																	59.12	60.12	1.00	C488374	152.0	950	35.1	57.91	60.93	3.02	1.38	46	0.00	0	FR	MS	30	30	3	3	ALS
																	60.12	60.54	0.42	C488375	226.0	825	46.0														
BX					SHL	DME	Bx	GY	60.12 - 64.61 m Sedimentary breccia, comprising subangular BK SHL clasts ranging from < 1 mm to 1.5 cm in avg. diameter; clasts are roughly equidimensional and float in a light grey matrix (dominantly siliceous)(I.e., matrix-supported, average space between clasts 1 - 5 mm); no obvious fabric; rare, subangular clasts of crystalline, mg white mineral (possibly feldspar). N.B. Very poor recovery in this interval.	w-f							60.54	60.96	0.42	C488376	315.0	475	45.1																						
																	60.96	64.01	3.05	C488377	248.0	362	34.0	60.93	64.01	3.08	0.16	5	0.00	0	FR	MS	20	30	3	3	ALS
																	64.01	64.31	0.30	C488378	195.5	403	36.7														
																	64.31	64.61	0.30	C488379	216.0	501	39.1														

PROPERTY: RICH **HOLE:** RI07-14A

Struct.		LITHOLOGY								ALT.			MINERALS				SAMPLES							Blocks			GEOTECHNICAL						JOINTS				
																											REC		ROD									
Type	Attitude	From (m)	To (m)	Interval (m)	Type	Unit	Texture	Modifier	Notes:				Ca	Sx	Fe	Ba	From (m)	To (m)	Interval (m)	Sample	Ni (ppm)	Zn (ppm)	Mo (ppm)	From (m)	To (m)	Intvl. (m)	(m)	Percent	(m)	Percent	Weathering	Hardness	Frequency	Attitude	Shape	Roughness	Infilling
BD	var	64.61	64.94	0.33	SHL	NIMO	LA	BK	64.61 - 64.94 m This is possibly where the NIMO Horizon should be, as this interval in underlain by calcareous BK SHL of the OSR, but no NIMO was visible, as core was v soft, altered to clay and v friable; clayey BK SHL, finely laminar and having a slightly waxy/greasy texture; rich in organic matter, and with common vfg Sx flecks; common, small (1 - 2 cm diam.) barite nodules and concentrically zoned, light-grey concretions (up to 1 cm diam) that do not fizz with HCl.	f				+		+	64.61	64.94	0.33	C488380	689.0	891	68.6	64.01	67.06	3.05	2.81	92	0.96	31	FR	MS	7	70	2	2	Cb
																		64.94	65.24	0.30	C488381	262.0	1080	63.7													
BD	80-8	64.94	82.30	17.36	SHL	OSR	LA	BK		w			+	+			65.24	65.54	0.30	C488382	221.0	609	52.7															
																	65.54	66.04	0.50	C488383	81.5	164	21.6															
																	66.04	66.54	0.50	C488385	130.0	347	33.0	67.06	70.10	3.04	2.50	82	0.45	15	FR	MS	10	10	3	2	Cb
																	66.54	67.54	1.00	C488386	116.5	364	30.0															
																	67.54	68.54	1.00	C488387	110.5	299	28.3															
																	68.54	69.54	1.00	C488388	82.8	199	19.7	70.10	73.15	3.05	2.86	94	0.35	11	FR	MS	20	20	3	2	Cb
																	69.54	71.04	1.50	C488389	147.5	367	35.9															
																	71.04	72.54	1.50	C488390	180.0	481	41.4															
																								73.15	76.20	3.05	2.93	96	0.29	10	FR	MS	10	10	1	1	Cb
																	BLANK			C488384	8.8	16	0.17															
																								76.20	79.25	3.05	3.01	99	1.99	65	FR	MS	2	2	1	1	Cb
																								79.25	82.30	3.05	2.95	97	2.07	68	FR	MS	2	2	1	1	Cb
		82.30							END OF HOLE																												

64.94 - 82.30 m Interval generally fines downward from GY-BK laminar SLT to BK SHL; interval starts with non-calcareous, finely laminar BK SHL that becomes calcareous and slightly harder/more competent @ 65.44 m , with recrystallization textures starting at 66.19 m; common-to-abundant calcareous GY SLT (finely to coarsely laminar) beds up to 70 cm thick in first 11 m of interval, and becoming less thick and uncommon-to-rare in last 7.5 m of interval; last 7.5 m of interval have dominantly v finely laminar, flat-bedded, hard and competent, calcareous BK SHL with common, flatly laminar Py bands up to 1.5 cm thick, parallel to BD. EOH

NiMo PROJECT

PROPERTY: Rich

HOLE: RI07-14B

Easting	Northing	Elev.	Depth (m)
444130	7357445		88.39

Contractor: North Star
Drill: MD-001

SURVEY							
Depth (m)	Azimuth	Dip	Method	Depth (m)	Azimuth	Dip	Method
collar	070°	-85°	compass				

Core size: BTW
Casing depth: 31.09 (m) out

Drilling dates: August 4 to 5, 2007

Logged by: D. MacDonald

Target: _____

SUMMARY				
From (m)	To (m)	Interval	Unit	Comments
0	33.53	33.53	OVB	
33.53	76.64	43.11	DME	
76.64	76.72	0.08	NiMo	very poor recovery, no visible NiMo
88.39	88.39	0	OSR	

SAMPLES	
Numbers:	C488337 - C488350
	no C488347
Total:	13
Date sent:	August 27, 2007

COMMENTS

Discrepency between drillers reported EOH (230') and last block in box (290')

PROPERTY: RICH **HOLE:** RI07-14B

Struct. Type	Struct. Attitude	LITHOLOGY From (m)	To (m)	Interval (m)	Type	Unit	Texture	Modifier	Notes:	ALT.			MINERALS Ca	Sx	Fe	Qz	SAMPLES From (m)	To (m)	Interval (m)	Sample	Ni (ppm)	Zn (ppm)	Mo (ppm)	Blocks From (m)	To (m)	Intvl. (m)	GEOTECHNICAL REC (m)	REC Percent	RQD (m)	RQD Percent	Weathering	Hardness	JOINTS Frequency	Attitude	Shape	Roughness	Infilling
		0.00	33.53	33.53	OVB				0 - 33.53 m Overburden																												
BD	80	33.53	76.64	43.11	SHL	DME	LA	BK						+	+	+																MW	W						
									33.53 - 76.64 m Interval starts with finely laminar, flat-bedded BK SHL that is highly fissile and moderately friable; BK SHL becomes more competent and slightly less fissile at about the 39 m mark; common, low-angle quartz veinlets (1 - 2 mm wide) mostly parallel to BD in first ~15 m of interval; uncommon limonite staining on fracture surfaces; rare Sx (Py) flecks in lower 1/3 of interval; BK SHL becomes finely interbedded with GY siliceous SLT beds and laminae (~3cm thick) at ~45 m mark until end of interval; abundance of SLT beds decreases with depth; at ~ 57 m, core becomes less competent and is slightly brecciated over last 4 m of interval.																																				
																								36.58	39.62	3.04	0.50	16	0.00	0	SW	W	20	60	2	2	
																								39.62	42.67	3.05	1.05	34	0.00	0	FR	W	15	50	2	2	
																								42.67	45.72	3.05	0.73	24	0.00	0	FR	MS	20	50	3	3	
																								45.72	48.77	3.05	2.15	70	0.00	0	FR	MS	15	60	2	2	
																								48.77	51.82	3.05	1.22	40	0.00	0	FR	MS	20	60	2	2	
																								51.82	54.87	3.05	1.44	47	0.00	0	FR	MS	20	60	2	2	
																								54.87	57.91	3.04	1.43	47	0.00	0	FR	MS	20	60	2	2	
																								57.91	60.93	3.02	1.08	36	0.00	0	FR	MS	20	60	2	2	
																								60.93	64.01	3.08	0.75	24	0.00	0	FR	MS	20	60	2	2	
									N.B. Region from about 64 m to 77.32 m shows extremely poor recovery, and therefore, sampling intervals are highly irregular for samples taken from this region.															64.01	67.06	3.05	0.44	14	0.00	0	FR	MS	30	60	2	2	
																								67.06	70.10	3.04	0.40	13	0.00	0	FR	MS	30	60	2	2	
																								70.10	73.15	3.05	0.14	5	0.00	0	FR	MS	30	60	2	2	
																	67.06	70.10	3.04	C488337	113.0	481	34.50														
																	70.10	73.15	3.05	C488338	106.0	155	28.40	73.15	76.20	3.05	0.15	5	0.00	0	FR	MS	30	60	2	2	
																	73.15	76.20	3.05	C488339	158.5	189	41.40														

PROPERTY: RICH **HOLE:** RI07-14B

Struct.		LITHOLOGY								ALT.			MINERALS				SAMPLES							Blocks			GEOTECHNICAL						JOINTS					
																											REC		RQD									
Type	Attitude	From (m)	To (m)	Interval (m)	Type	Unit	Texture	Modifier	Notes:				Ca	Sx	Fe	Qz	From (m)	To (m)	Interval (m)	Sample	Ni (ppm)	Zn (ppm)	Mo (ppm)	From (m)	To (m)	Intvl. (m)	(m)	Percent	(m)	Percent	Weathering	Hardness	Frequency	Attitude	Shape	Roughness	Infilling	
																	76.20	76.64	0.44	C488340	163.5	418	36.10															
BD	80	76.64	76.72	0.08	SHL	NIMO	LA	BK	76.64 - 77.32 m Highly fractured and weathered BK SHL, v. clayey; suspect this is where NIMO Horizon should be stratigraphically, but no visible signs of it (no Sx or associated alteration products). N.B. Huge recovery problems here.	f							76.64	77.82	1.18	C488341	451.0	965	73.60	76.20	79.25	3.05	2.22	73	1.53	50	FR	MS	2	70	1	1		
BD	80	77.32	78.46	1.14	SHL	OSR	LA	BK	77.32 - 78.46 m Finely laminar, flat-bedded SHL, darker and much more competent, less weathered and less fissile than BK SHLs in above intervals, becoming calcareous and slightly recrystallized at 77. 47 m. Rare barite nodules ~2.5 cm in diameter.	w			+				77.82	78.46	0.64	C488342	152.0	394	46.00															
BD	45-85				LST	OSR	LA	GY	78.46 - 78.96 m Inclined-bedded, fg GY sandy SLT/LST that fines downwards.	w			+																										
BD	70				SHL	OSR	LA	BK		w			+	+			78.46	78.96	0.50	C488343	13.9	32	6.82	79.25	82.30	3.05	2.94	96	2.10	69	FR	MS	3	10	1	1		
																	78.96	79.96	1.00	C488344	87.6	289	27.40															
									78.96 - 88.39 m EOH V finely laminar, calcareous BK SHL with inclined bedding, interbedded with GY calcareous, slightly sandy SLT beds up to 15 cm thick, with some erosional scouring at bases of beds; common Sx (Py) lenses up to 2 cm diam; BK SHL becomes slightly darker with depth; interval ends with 2 small brecciated zones about 30 cm wide each, with v angular BK SHL clasts up to 5 cm x 2 cm, floating in a calcite matrix.								79.96	80.96	1.00	C488345	90.7	337	28.20															
																	80.96	81.96	1.00	C488346	94.4	278	29.00	82.30	85.34	3.04	2.85	94	2.23	73	FR	MS	2	70	1	1		
																	81.96	83.46	1.50	C488349	120.0	255	34.60															
																	83.46	84.96	1.50	C488350	134.0	287	37.60															
																	BLANK			C488348	<0.2	15	0.28	85.34	88.39	3.05	3.10	102	2.29	75	FR	MS	4	70	1	1		
									EOH																													
		88.39							END OF HOLE																													

NiMo PROJECT

PROPERTY: Rich

HOLE: RI07-15

Easting	Northing	Elev.	Depth (m)
443631	7358223	643	124.97

Contractor: North Star
Drill: MD-002

SURVEY							
Depth (m)	Azimuth	Dip	Method	Depth (m)	Azimuth	Dip	Method
collar	060°	-60°	compass				

Core size: BTW
Casing depth: 36.58 (m) out

Drilling dates: July 30 to 31, 2007

Logged by: D. MacDonald

Target: _____

SUMMARY				
From (m)	To (m)	Interval	Unit	Comments
0.00	38.50	38.50	OVB	
38.50	101.50	63.00	DME	
101.50	101.53	0.03	NiMo	
101.53	124.97	23.44	OSR	

SAMPLES

Numbers: C488314 - C488336

Total: 23
Date sent: August 16, 2007

COMMENTS

PROPERTY: RICH **HOLE:** RI07-15

Struct.		LITHOLOGY								ALT.			MINERALS				SAMPLES							Blocks			GEOTECHNICAL						JOINTS				
																											REC		RQD									
Type	Attitude	From (m)	To (m)	Interval (m)	Type	Unit	Texture	Modifier	Notes:				Ca	Sx	Fe	Qz	From (m)	To (m)	Interval (m)	Sample	Ni (ppm)	Zn (ppm)	Mo (ppm)	From (m)	To (m)	Intvl. (m)	(m)	Percent	(m)	Percent	Weathering	Hardness	Frequency	Attitude	Shape	Roughness	Infilling
		0.00	38.50	38.50	OVB				Overburden																											
BD	80	38.50	101.50	63.00	SHL	DME	LA	BK		w			+	+										39.28	39.62	0.34	0.37	109	0.00	0	SW	W	30	90	2	2	
									38.50 - 56.09 m Dominantly finely laminar BK SHL (flat-bedded) that is moderately fissile parallel to bedding, very finely interbedded with abundant GY-BK siliceous SLT that shows both flat and inclined bedding; BK SHL and GY-BK SLT have subtle gradational contacts, mostly conformable; BK SHL also interbedded with rare, calcareous GY SLT beds up to ~10 cm thick; rare blebs of Sx (Py) 1 mm x 2 mm, parallel to bedding; almost no veinlets; abundance of GY SLT beds increases with depth.												39.62	42.67	3.05	3.14	103	0.38	12	SW	MS	20	80	2	2	ALS
																								42.67	45.72	3.05	2.63	86	0.00	0	FR	MS	20	70	2	2	ALS
																								45.72	48.77	3.05	2.99	98	0.20	7	FR	MS	15	80	2	2	ALS
																								48.77	51.82	3.05	3.33	109	0.10	3	FR	MS	15	80	2	2	ALS
																								51.82	54.87	3.05	2.54	83	0.41	13	FR	MS	16	80	2	2	ALS
																								54.87	57.91	3.04	2.67	88	0.22	7	FR	MS	15	60	3	2	ALS
BD	80-70				SHL	DME	LA	BK	56.09 - 64.12 m Same interbedded BK SHL and GY SLT as in previous interval, except this interval exhibits abundant quartz veinlets up to 1 cm wide, mostly parallel to bedding, and constituting mildly-to-moderately brecciated regions up to ~1 m wide; core becomes slightly porous, corroded and soft over the last 1 m of the interval	w-f			+			+																		
																								57.91	60.93	3.02	2.97	98	0.23	8	FR	MS	10	60	5	3	Qz
																								60.93	64.01	3.08	2.63	85	0.30	10	FR	MS	10	60	2	2	Qz

PROPERTY: RICH **HOLE:** RI07-15

Struct.		LITHOLOGY								ALT.			MINERALS				SAMPLES							Blocks			GEOTECHNICAL						JOINTS				
																											REC		RQD									
Type	Attitude	From (m)	To (m)	Interval (m)	Type	Unit	Texture	Modifier	Notes:				Ca	Sx	Fe	Qz	From (m)	To (m)	Interval (m)	Sample	Ni (ppm)	Zn (ppm)	Mo (ppm)	From (m)	To (m)	Intvl. (m)	(m)	Percent	(m)	Percent	Weathering	Hardness	Frequency	Attitude	Shape	Roughness	Infilling
BD	80-85				SHL	DME	LA	BK	64.12 - 72.38 m Finely laminar BK SHL (flat-bedded), v finely interbedded with GY-BK siliceous SLT (slightly sandy) that shows common, wavy-to-flat laminae; both SHL and SLT beds average 2 - 8 cm thickness; Sx absent in this interval; common quartz veinlets parallel to bedding uncommon in upper 4 m of interval, becoming more common in the middle of the interval; abundance of GY SLT beds increases with depth; interval coarsens downward in general.	w						+										64.01	67.06	3.05	2.24	73	0.22	7	FR	MS	12	80	2	2	ALS
																								67.06	70.10	3.04	2.80	92	0.24	8	FR	MS	10	80	2	2	Cb
																								70.10	73.15	3.05	2.76	90	0.00	0	FR	MS	15	70	2	2	Cb
BD	50-80				SHL	DME	LA	BK		w			+											73.15	76.20	3.05	2.75	90	0.44	14	FR	MS	15	60	2	2	ALS
									72.38 - 85.46 m Finely laminar, inclined-to-flat bedded BK SHL finely interbedded with laminar GY sandy SLT (near top of interval) to GY fg SS (at bottom of interval); rare GY calcareous SLT beds up to ~20 cm thick are relatively evenly distributed across the whole interval; interval coarsens downward and becomes less well-bedded.															76.20	79.25	3.05	2.37	78	0.30	10	FR	MS	10	80	2	2	ALS
																								79.25	82.30	3.05	2.75	90	0.56	18	FR	MS	10	80	2	2	ALS
																								82.30	85.34	3.04	3.00	99	0.85	28	FR	MS	10	80	2	2	ALS
BD	80				SHL	DME	LA	BK		w				+										85.34	88.39	3.05	3.03	99	0.80	26	FR	MS	9	80	2	2	ALS
									85.46 - 98.14 m Finely laminar BK SHL interbedded with common-to-abundant GY-BK siliceous SLT; core becomes less competent and slightly soft over the last 1 - 1.5 m of the interval (especially true of the BK SHL); v rare Py flecks and blebs (1mm x 1mm).													88.39	91.44	3.05	2.86	94	0.96	31	FR	MS	8	80	2	2	ALS
																								91.44	94.49	3.05	3.08	101	0.42	14	FR	MS	12	80	2	2	ALS
																	93.90	95.40	1.50	C488314	135.0	628	49.0	94.49	97.54	3.05	3.00	98	0.00	0	FR	MS	20	80	2	2	ALS
																	95.40	96.90	1.50	C488315	148.0	520	46.2														
																	96.90	97.90	1.00	C488316	124.5	238	35.8	97.54	100.58	3.04	1.48	49	0.00	0	FR	W	20	80	2	2	ALS
BD	80				SHL	DME	LA	BK	98.14 - 100.67 m Same lithologies as in previous interval, except that core becomes moderately brecciated; GY SLT beds decrease slightly in abundance relative to previous interval.	w-f					+			97.90	98.90	1.00	C488317	131.5	180	37.4																
																	98.90	99.90	1.00	C488318	133.5	189	44.1														
BD	80				SHL	DME	LA	BK	100.67 - 101.50 m Moderately weathered and highly fractured BK SHL as in previous interval; poor recovery in this interval, which ends in clayey SHL + minor possible fault gouge	m								99.90	100.40	0.50	C488319	172.0	162	58.8	100.58	103.63	3.05	2.70	89	1.35	44	FR	MS	9	80	2	2	Cb
BD	var	101.50	101.53	0.03	SX	NIMO	LA/I	BZ	101.50 - 101.53 m NIMO Horizon; estimated 3 cm thick; bronze, finely laminar, moderately bioturbated Sx in BK SHL host; interval was broken up in core barrel, therefore, thickness is estimated.	w					+			100.40	100.90	0.50	C488320	165.5	127	59.7																
BD	80	101.53	124.97	23.44	SHL	OSR	LA	BK	101.53 - 101.92 m Clayey, altered BK SHL, non-calcareous, laminar; severe recovery problem in this interval (fault gouge ~2 cm thick, clay + silt).	f								100.90	101.20	0.30	C488321	162.5	323	49.4														
BA					BAL	OSR	BA	GY	101.92 - 102.28 m Limestone ball, internally brecciated (calcite matrix veinlets up to 0.5 cm wide)	w				+				101.20	101.50	0.30	C488322	155.0	316	40.0	103.63	106.68	3.05	3.12	102	2.73	90	FR	MS	1	80	2	2	Cb
BD	85				SHL	OSR	LA	BK		w				+	+			101.50	101.53	0.03	C488323	2.66%	3800	2790														

PROPERTY: RICH **HOLE:** RI07-15

Struct.		LITHOLOGY								ALT.			MINERALS				SAMPLES								Blocks			GEOTECHNICAL							JOINTS				
																												REC		RQD									
Type	Attitude	From (m)	To (m)	Interval (m)	Type	Unit	Texture	Modifier	Notes:				Ca	Sx	Fe	Qz	From (m)	To (m)	Interval (m)	Sample	Ni (ppm)	Zn (ppm)	Mo (ppm)	From (m)	To (m)	Intvl. (m)	(m)	Percent	(m)	Percent	Weathering	Hardness	Frequency	Attitude	Shape	Roughness	Infilling
									102.28 - 122.91 m Finely laminar, flat-bedded BK SHL interbedded with common calcareous GY sandy SLT beds up to ~30 cm thick (fining upwards) with generally sharp basal contacts in the GY SLT; BK SHL darkens at about ~107.05 m, and shows recrystallization textures from 102.75 m until EOH; common Sx (Py) bands up to 1 cm thick.								BLANK			C488324	2.6	16	0.4															
																	101.53	101.92	0.39	C488325	611.0	1025	112.5	106.68	109.73	3.05	2.93	96	1.86	61	FR	MS	3	80	2	2	Cb
																	101.92	102.28	0.36	C488326	38.2	124	9.4															
																	102.28	102.78	0.50	C488327	113.0	316	32.9															
																	102.78	103.28	0.50	C488328	104.5	246	29.9	109.73	112.78	3.05	3.00	98	1.40	46	FR	MS	2	30	2	2	Cb
																	103.28	104.28	1.00	C488329	115.0	378	32.7															
																	104.28	105.28	1.00	C488330	112.5	343	31.6															
																	105.28	106.28	1.00	C488331	118.5	319	30.9	112.78	115.83	3.05	3.05	100	2.48	81	FR	MS	2	30	2	2	Cb
																	106.28	107.78	1.50	C488332	148.0	281	38.2															
																	107.78	109.28	1.50	C488333	190.0	504	43.2															
																								115.83	118.87	3.04	3.03	100	2.75	90	FR	MS	1	30	2	2	Cb
																								118.87	121.92	3.05	3.08	101	2.01	66	FR	MS	2	30	2	2	Cb
BD	85				SHL	OSR	LA	BK	122.91 - 124.97 m V finely laminar BK calcareous SHL, v. dark, hard and organic-rich, as well as producing strong H2S odour with HCl; uncommon Sx (Py) beds up to 2.5 cm thick and parallel to bedding, fining downwards (fg at top to vfg at bottom); BK SHL v competent.	w			+	+												121.92	124.97	3.05	3.10	102	1.99	65	FR	MS	1	80	2	2	Cb
																	124.34	124.64	0.30	C488334	163.0	244	54.1															
																	124.64	124.67	0.03	C488335	38.4	12	8.65															
		124.97							END OF HOLE								124.67	124.97	0.30	C488336	156.0	172	53.6															

NiMo PROJECT

PROPERTY: Rich

HOLE: RI07-16

Easting	Northing	Elev.	Depth (m)
443054	7359059		121.92

Contractor: North Star
Drill: MD-002

SURVEY							
Depth (m)	Azimuth	Dip	Method	Depth (m)	Azimuth	Dip	Method
collar	060°	-75°	compass				

Core size: BTW
Casing depth: 30.48 (m) out

Drilling dates: August 9 to 10, 2007

Logged by: J. Lane

Target: _____

SUMMARY				
From (m)	To (m)	Interval	Unit	Comments
0.00	16.02	16.02	OVB	
16.02	91.90	75.88	DME	
91.90	91.91	0.01	NiMo	
91.91	121.92	30.01	OSR	

SAMPLES

Numbers: C488403 - C488414

Total: 12
Date sent:

COMMENTS

PROPERTY: RICH **HOLE:** RI07-16

LITHOLOGY										ALT.			MINERALS				SAMPLES							Blocks			GEOTECHNICAL						JOINTS				
Struct.																											REC		RQD								
Type	Attitude	From (m)	To (m)	Interval (m)	Type	Unit	Texture	Modifier	Notes:	als			py	car	cpy		From (m)	To (m)	Interval (m)	Sample	Ni (ppm)	Zn (ppm)	Mo (ppm)	From (m)	To (m)	Intvl. (m)	(m)	Percent	(m)	Percent	Weathering	Hardness	Frequency	Attitude	Shape	Roughness	Infilling
		0.00	16.02	16.02	OVB				overburden																												
BD	60	16.02	54.02	38.00	SHL	DME	FG	BK	The core is very hard- cherty, it is generally black in colour and is very fine grained NOTE: from 16.02-24.38, the core is slightly softer. Very thin lamina (<1mm) of pyrite are present and spaced 3-4mm apart throughout the core. Slightly coarser grained shale occurs in generally 2-3 cm thickness (but occurs up to 10cm),is intermittent within the shale and can contain pyrite lamina. Blebs of pyrite also occur throughout the black shale. Aluminosilicate occurs as a white powder on the fractured surfaces. 2-3cm thick quartz veins occur running parallel to bedding (generally) but also see some very thin quartz veinlets perpendicular to bedding (tension filled?)	m			m												16.02	18.24	2.22	2.27	102	0.00	0	SW	S	15	80	1	2	ALS
																								18.28	21.35	3.07	2.84	93	0.60	20	FR	S	10	70	1	2	ALS
													w	w																							
									19.29-20.11: carbonaceous rock containing circular nodules ~1cm in diameter with pyrite and some chalcopyrite visible within.															21.35	24.38	3.03	3.20	106	0.35	12	FR	S	12	70	1	2	ALS
																								24.38	27.43	3.05	2.84	93	0.24	8	FR	S	15	70	1	2	ALS
																								27.43	30.48	3.05	2.24	73	0.44	14	FR	S	13	70	1	2	ALS
																								30.48	33.53	3.05	2.93	96	0.11	4	FR	S	14	70	1	2	ALS
																								33.53	36.58	3.05	2.47	81	0.55	18	FR	S	9	70	1	2	ALS
																								36.58	39.62	3.04	2.55	84	0.10	3	FR	S	12	60	1	2	ALS
																								39.62	42.67	3.05	2.63	86	0.11	4	FR	S	14	60	1	2	ALS
																								42.67	45.72	3.05	2.70	89	0.11	4	FR	S	14	60	1	2	ALS
																								45.72	48.77	3.05	2.93	96	0.39	13	FR	S	12	60	1	2	ALS
																								48.77	51.82	3.05	2.98	98	0.48	16	FR	S	9	60	1	2	ALS
																								51.82	54.87	3.05	2.95	97	0.67	22	FR	S	9	60	1	2	ALS

PROPERTY: RICH **HOLE:** RI07-16

Struct. Type	Struct. Attitude	LITHOLOGY From (m)	To (m)	Interval (m)	Type	Unit	Texture	Modifier	Notes:	ALT. als			MINERALS py	car	cpy		SAMPLES From (m)	To (m)	Interval (m)	Sample	Ni (ppm)	Zn (ppm)	Mo (ppm)	Blocks From (m)	To (m)	Intvl. (m)	GEOTECHNICAL REC (m)	REC Percent	RQD (m)	RQD Percent	Weathering	Hardness	JOINTS Frequency	Attitude	Shape	Roughness	Infilling
		54.02	57.41	3.39	CBR	DME	FG	GY	fine grained light to medium grey carbonaceous shale containing a few thin (<1mm) carbonate veinlets, upper and lower contacts are gradational. Similar carbonate horizons occur intermixed within the black shale in generally 20 cm spacing.					st										54.87	57.91	3.04	2.96	97	0.11	4	FR	S	12	50	1	2	ALS
		57.41	77.27	19.86	SHL	DME	FG	BK	the shale has become quite organic rich with graphitic like surfaces to the fractures. 65.80-65.82 - pyrite layers are starting to occur in the core which are internally laminated and slightly swaley, similar to the NiMo- but only composed of pyrite. In general the core does not contain as much pyrite as the thin pyrite laminations have decreased in concentration.				tr													57.91	60.93	3.02	2.84	94	0.91	30	FR	S	6	60	1	2	ALS
																								60.93	64.01	3.08	1.40	45	0.00	0	FR	S	9	60	1	2	ALS
																								64.01	67.06	3.05	3.25	107	0.76	25	FR	S	10	60	1	2	ALS
																								67.06	70.10	3.04	2.98	98	0.74	24	FR	S	7	10	1	2	ALS
																								70.10	73.15	3.05	2.94	96	0.96	31	FR	S	8	60	1	2	ALS
																								73.15	76.20	3.05	2.95	97	0.49	16	FR	S	11	60	1	2	ALS
																								76.20	79.25	3.05	2.80	92	0.31	10	FR	S	11	60	1	2	Qz
		77.27	77.39	0.12	CBR	DME	FG	GY	carbonaceous horizon medium to light grey in colour					st																								
		77.39	91.90	14.51	SHL	DME	FG	BK	similar shale as above; at 83.26 sulphide layer somewhat granular looking occurs . Core becomes very blocky and irregularly broken up at around 87.09. Broken and fractured surfaces show white aluminosilicate powder on them.	st																79.25	82.30	3.05	2.68	88	0.75	25	FR	S	10	60	1	2	Qz
																								82.30	85.34	3.04	3.08	101	0.67	22	FR	S	11	60	1	2	Qz
																								85.34	88.39	3.05	2.97	97	0.10	3	FR	S	30	60	1	2	Qz
																	86.50	88.00	1.50	C488403	146.0	152	50.3														
																	88.00	89.50	1.50	C488404	158.5	129	54.7														
																	89.50	90.44	0.94	C488405	193.0	159	74.7	88.39	91.44	3.05	2.00	66	0.00	0	FR	S	30	60	1	2	Qz
																	90.44	91.44	1.00	C488406	149.5	369	43.2														
																	91.44	91.90	0.46	C488407	735.0	594	54.9														
		91.90	91.91	0.01	MSX	NiMo			1.0-1.5cm thick quite broken up and fractured looking with visible displacement of 1cm occurring on flat slip surface. The top 0.5 cm is quite massive looking with quite planar laminations, while the bottom 0.5 cm is much more disturbed looking with swaly bedding and an even granular looking texture.								91.90	91.91	0.01	C488408	4.56%	1.05%	2890	91.44	94.49	3.05	2.76	90	1.42	47	FR	MS	4	60	1	2	Cb
		91.91	92.54	0.63	SHL	OSR	FG	BK	Noticeably softer shale that is black in colour. May contain barite nodules- can see lens shaped somewhat granular looking nodules within the shale, also the core is quite heavy. The core begins to fizz slightly at 92.31.								91.91	92.54	0.63	C488409	263.0	654	79.5														
		92.54	94.48	1.94	LBM	OSR	RG	GY	layered light grey coloured very carbonaceous rock. The rock is quite hard showing some very thin carbonate veinlets; there is some visible internal structure at 93.88 which almost looks like cross bedding.					st			92.54	93.27	0.73	C488411	135.0	435	33.8														
		94.48	121.92	27.44	SHL	OSR	FG	BK	The core has become very hard, almost								93.27	94.48	1.21	C488412	22.4	38	7.1	94.49	97.54	3.05	3.03	99	1.74	57	FR	MS	2	30	1	2	Cb
																	94.48	96.00	1.52	C488413	109.0	359	31.2														

PROPERTY: RICH **HOLE:** RI07-16

Struct.		LITHOLOGY								ALT.			MINERALS				SAMPLES							Blocks			GEOTECHNICAL						JOINTS				
																											REC		RQD									
Type	Attitude	From (m)	To (m)	Interval (m)	Type	Unit	Texture	Modifier	Notes:	als			py	car	cpy		From (m)	To (m)	Interval (m)	Sample	Ni (ppm)	Zn (ppm)	Mo (ppm)	From (m)	To (m)	Intv/. (m)	(m)	Percent	(m)	Percent	Weathering	Hardness	Frequency	Attitude	Shape	Roughness	Infilling
									The core has become very hard- almost chert like. The shale is black in colour, contains pyrite blebs to 3mm by 1.5cm in size that are sometimes surrounded by a thin layer of carbonate, carbonate veinlets running parallel to bedding also occurs. The core fizzes moderately. Around the 96.67 the core gradually becomes softer, there does not however seem to be any noticeable change in the reaction of the rock to acid. Core is quite massive with few natural breaks, In general the core is quite uniform until the end of the hole; there is however a section from 113.68-113.78 of a coarser grained layered carbonate. Also large (1cm) pyrite @ 155.37 has blurry upper contacts and a sharp lower contact.								96.00	97.54	1.54	C488414	98.4	314	27.1																
																	BLANK			C488410	10.8	25	1.53	97.54	100.58	3.04	2.97	98	2.23	73	FR	MS	3	30	1	2	Cb
																								100.58	103.63	3.05	3.25	107	1.84	60	FR	MS	9	70	1	2	Cb
																								103.63	106.68	3.05	3.09	101	0.98	32	FR	MS	9	40	1	2	Cb
																								106.68	109.73	3.05	2.94	96	1.42	47	FR	MS	11	70	1	2	Cb
																								109.73	112.78	3.05	3.07	101	1.53	50	FR	MS	3	60	1	2	Cb
																								112.78	115.83	3.05	2.98	98	1.95	64	FR	MS	2	60	1	2	Cb
																								115.83	118.87	3.04	0.68	22	0.00	0	FR	MS	3	30	1	2	Cb
																								118.87	121.92	3.05	2.25	74	0.54	18	FR	MS	13	60	1	2	Cb
		121.92							END OF HOLE!																												

NiMo PROJECT

PROPERTY: Rich

HOLE: RI07-17

Easting	Northing	Elev.	Depth (m)
443467	7358361	608	121.92

Contractor: North Star
Drill: MD-002

SURVEY							
Depth (m)	Azimuth	Dip	Method	Depth (m)	Azimuth	Dip	Method
collar	060°	-60°	compass				

Core size: BTW
Casing depth: 33.23 (m) out

Drilling dates: August 1 to 2, 2007

Logged by: D. MacDonald

Target: _____

SUMMARY				
From (m)	To (m)	Interval	Unit	Comments
0.00	21.34	21.34	OVB	
21.34	96.74	75.40	DME	
96.74	96.75	0.01	NiMo	
96.75	121.92	25.17	OSR	

SAMPLES	
Numbers:	C488294 - C488313
Total:	20
Date sent:	August 16, 2007

COMMENTS

PROPERTY: RICH **HOLE:** RI07-17

Struct. Type	Struct. Attitude	LITHOLOGY From (m)	LITHOLOGY To (m)	LITHOLOGY Interval (m)	LITHOLOGY Type	LITHOLOGY Unit	LITHOLOGY Texture	LITHOLOGY Modifier	Notes:	ALT.	MINERALS Ca	MINERALS Sx	MINERALS Fe	SAMPLES From (m)	SAMPLES To (m)	SAMPLES Interval (m)	SAMPLES Sample	SAMPLES Ni (ppm)	SAMPLES Zn (ppm)	SAMPLES Mo (ppm)	Blocks From (m)	Blocks To (m)	Blocks Int/l. (m)	GEOTECHNICAL REC (m)	GEOTECHNICAL REC Percent	GEOTECHNICAL RQD (m)	GEOTECHNICAL RQD Percent	GEOTECHNICAL Weathering	GEOTECHNICAL Hardness	JOINTS Frequency	JOINTS Attitude	JOINTS Shape	JOINTS Roughness	JOINTS Infilling
		0.00	21.34	21.34	OVB				Overburden																									
BD	80	21.34	96.74	75.40	SHL	DME	LA	BK	21.34 - 63.51 m Finely laminar, slightly fissile flat-bedded BK SHL with limonite staining in uncommon (3) zones 10 - 15 cm wide; BK SHL interbedded with common GY silty-to-vfg sandy SLT beds ranging in thickness from 1 cm to 15 cm; rare calcite veinlets (1 mm) parallel to bedding and uncommon Sx (Py) bands up to 2 mm wide.	w		+	+	+												21.35	36.58	15.23	2.63	17	0.00	0	MW	MS	10	80	2	2	GYP
																					36.58	39.62	3.04	2.90	95	0.20	7	SW	MS	10	80	2	2	Li
																					39.62	42.67	3.05	3.03	99	0.43	14	SW	MS	8	30	2	2	GYP
																					42.67	45.72	3.05	3.05	100	0.45	15	FR	MS	10	80	2	2	GYP
																					45.72	48.77	3.05	3.02	99	0.22	7	FR	MS	13	80	2	2	GYP
																					48.77	51.82	3.05	2.98	98	0.10	3	FR	MS	13	80	2	2	GYP
																					51.82	54.87	3.05	3.08	101	0.00	0	FR	MS	15	80	2	2	GYP
																					54.87	57.91	3.04	2.90	95	0.11	4	FR	MS	14	80	2	2	GYP
																					57.91	60.93	3.02	2.15	71	0.00	0	FR	MS	14	70	2	2	Li
																					60.93	64.01	3.08	2.59	84	0.38	12	FR	MS	15	60	2	2	GYP
BD	var				LST	DME	LA	GY	63.51 - 65.56 m Generally coarsening downwards, finely wavy laminar GY silty-cg sandy LST that has disrupted bedding in last 10 - 15 cm of interval; erosional (scoured) basal contact.	w		+														64.01	67.06	3.05	3.06	100	1.40	46	FR	MS	7	80	2	2	Cb
BD	85				SHL	DME	LA	BK	65.56 - 69.85 m Scoured upper contact into finely laminar silty BK SHL, interbedded with common, finely laminar GY SLT beds up to 3 cm thick; interval fines downward to BK SHL (mudstone); rare Py flecks.	w			+												67.06	70.10	3.04	2.40	79	0.30	10	FR	MS	10	80	2	2	GYP

PROPERTY: RICH **HOLE:** RI07-17

Struct.		LITHOLOGY								ALT.			MINERALS				SAMPLES								Blocks			GEOTECHNICAL						JOINTS				
																												REC		RQD								
Type	Attitude	From (m)	To (m)	Interval (m)	Type	Unit	Texture	Modifier	Notes:				Ca	Sx	Fe		From (m)	To (m)	Interval (m)	Sample	Ni (ppm)	Zn (ppm)	Mo (ppm)	From (m)	To (m)	Int/l. (m)	(m)	Percent	(m)	Percent	Weathering	Hardness	Frequency	Attitude	Shape	Roughness	Infilling
BD	80				LST	DME	LA	GY	69.85 - 71.02 m Thick, finely bedded GY silty LST, with slightly wavy laminae up to 3 mm thick; sharp, erosional bottom contact.	w			+																										
																								70.10	73.15	3.05	2.97	97	0.72	24	FR	MS	10	70	2	2	Cb
BD	80				SHL	DME	LA	BK		w			+	+																								
																								73.15	76.20	3.05	2.83	93	0.21	7	FR	MS	12	70	1	2	GYP
									71.02 - 96.74 m Interval starts with finely laminar, non-calcareous BK SHL interbedded with common GY SLT (fining upwards) beds up to several cm thick with slightly inclined bedding and rare X-stratification; rare, thin, flatly laminar Sx (Py) bands 1 - 2 mm thick parallel to BD; GY SLT beds become slightly thinner (down to 1 - 2 cm) and slightly less abundant with increasing depth; rare, thin (2 cm) beds of calcareous GY slightly-sandy SLT; rare calcite veinlets (< 1mm) in last 3 m of interval.																														
																								76.20	79.25	3.05	3.03	99	0.32	10	FR	MS	10	70	1	2	GYP
																								79.25	82.30	3.05	1.55	51	0.00	0	FR	MS	18	70	1	2	GYP
																								82.30	85.34	3.04	1.20	39	0.00	0	FR	MS	18	70	1	2	GYP
																								85.34	88.39	3.05	2.91	95	0.44	14	FR	MS	12	80	1	2	GYP
																	BLANK			C488297	2.5	16	0.3	88.39	91.44	3.05	3.00	98	2.15	70	FR	MS	2	80	1	2	GYP
																	89.04	90.54	1.50	C488294	127.0	687	46.8														
																	90.54	92.04	1.50	C488295	167.5	397	48.7	91.44	94.49	3.05	3.08	101	0.35	11	FR	MS	13	80	1	2	Qz
																	92.04	93.04	1.00	C488296	156.0	313	44.1														
																	93.04	94.04	1.00	C488298	151.5	237	47.8	94.49	97.54	3.05	2.73	90	0.42	14	FR	MS	20	80	1	2	GYP
																	94.04	95.04	1.00	C488299	157.5	220	49.6														
BD	75-8	96.74	96.75	0.01	SX	NIMO	LA/I	BZ	96.74 - 96.75 m Slightly less than 1 cm thick, wavy laminar, bioturbated, bronze Sx bed; N.B. sample is crushed to rubble, so the 'way up' is not known; minor fault gouge occurs just below the NIMO Horizon.	w				+		95.04	95.54	0.50	C488300	323.0	630	63.6														
BD	80	96.75	121.92	25.17	SHL/S	OSR	LA	BK	96.75 - 96.88 m Finely laminar, GY-BK non-calcareous SHL which becomes silty in last 6 cm of interval; slightly inclined bedding	w						95.54	96.04	0.50	C488301	166.0	465	43.4	97.54	100.58	3.04	2.78	91	1.11	37	FR	MS	6	70	1	2	Cb
BA					BAL	OSR	Bx	GY	96.88 - 97.39 m fg GY LSY ball, that is internally slightly brecciated with randomly oriented calcite veinlets up to 1 cm thick.	w			+			96.04	96.34	0.30	C488302	269.0	750	60.2														
BD	85				SHL	OSR	LA	BK	97.39 - 97.55 m Fractured, non-calcareous laminar BK SHL, altered in part to clay.	w-f						96.34	96.74	0.40	C488303	242.0	829	39.3														
BD	85				LST	LST	LA	GY	97.55 - 97.91 m Finely laminar GY silty LST (almost fg SS), wavy laminated.	w			+			96.74	96.75	0.01	C488304	7.04%	1.54%	2560	100.58	103.63	3.05	3.06	100	2.26	74	FR	MS	2	80	1	2	Cb
BD	85				SHL/S	OSR	LA	BK	97.91 - 100.91 m Finely laminar BK calcareous SHL (flat-bedded) interbedded with finely and slightly wavy laminar GY silty LST (slightly inclined bedding); interval comprises 2 coarsening downward cycles (MST to SLT to fg SS), each being about 1.5 m thick; rare, high-angle calcite veinlets ~1mm thick; v rare Sx (Py) blebs (1mm x 1mm). N.B. Slight recrystallization textures or fresh fracture surfaces after 97 + m.	w			+	+		96.75	97.05	0.30	C488305	308.0	344	28.0														
BD	80				SHL/S	OSR	LA	BK	100.91 - 110.19 m Interval starts with finely laminar, calcareous BK SHL and coarsens downward in general; after ~102 m , BK SHL becomes interbedded with abundant GY silty LST (flat-to-slightly-inclined bedding); core changes colour slightly to DK GY over last 3/4 of the interval; common Py lenses up to ~1 cm thick, parallel to BD.	w			+	+		97.05	97.35	0.30	C488306	32.7	87	8.9														
																	97.35	97.85	0.50	C488307	94.4	307	21.5	103.63	106.68	3.05	3.06	100	1.67	55	FR	MS	2	80	1	2	Cb
																	97.85	98.35	0.50	C488308	149.0	336	25.3														
																	98.35	99.35	1.00	C488309	152.0	453	32.2														
																	99.35	100.35	1.00	C488310	145.0	499	29.2	106.68	109.73	3.05	3.02	99	2.63	86	FR	MS	1	30	1	2	Cb
																	100.35	101.35	1.00	C488311	119.0	360	29.1														

PROPERTY: RICH **HOLE:** RI07-17

LITHOLOGY										ALT.			MINERALS				SAMPLES							Blocks			GEOTECHNICAL						JOINTS				
Struct.																											REC		RQD								
Type	Attitude	From (m)	To (m)	Interval (m)	Type	Unit	Texture	Modifier	Notes:				Ca	Sx	Fe		From (m)	To (m)	Interval (m)	Sample	Ni (ppm)	Zn (ppm)	Mo (ppm)	From (m)	To (m)	Intvl. (m)	(m)	Percent	(m)	Percent	Weathering	Hardness	Frequency	Attitude	Shape	Roughness	Infilling
																	101.35	102.85	1.50	C488312	130.5	286	34.3														
																	102.85	104.35	1.50	C488313	153.5	261	41.4	109.73	112.78	3.05	2.99	98	2.94	96	FR	MS	1	5	1	2	Cb
BD	85				SHL	OSR	LA	BK		w			+	+																							
									110.19 - 118.50 m Finely laminar, flat-bedded, calcareous BK SHL; interval starts with rare vfg GY silty LST, which become more common with increasing depth; interval coarsens downward in general with sharp upper and lower contacts (bottom contact slightly erosional; core v hard and competent; no veining; rare Sx (Py) lenses up to ~1cm thick.																																
																								112.78	115.83	3.05	2.99	98	1.89	62	FR	MS	2	40	1	2	Cb
																								115.83	118.87	3.04	2.20	72	0.37	12	FR	MS	6	80	1	2	Cb
BD	85				LST	OSR	LA	GY	118.50 - 119.34 m V finely laminar, flat-bedded, GY silty LST with gradational lower contact (~1 cm), conformable to underlying SHL; several Py bands (~1 cm thick) and rare lenses, parallel to BD; LST fines downwards.	w			+	+										118.87	121.92	3.05	3.02	99	2.17	71	FR	MS	3	50	1	2	Cb
BD	85				SHL	OSR	LA	BK	119.34 - 121.92 m (EOH) Finely laminar, calcareous BK SHL, almost massive; v hard and recrystallized through most of interval; rare calcite veinlets ~45 degrees to BD, 1 mm max. thickness; rare calcite veinlets up to 1 cm thick parallel to bedding; v rare, finely laminar GY silty LST beds (several mm to 1 cm thick); strong H2S odour with HCl; rare flecks of fg Py. EOH	w			+	+																										
		121.92							END OF HOLE																													

NiMo PROJECT

PROPERTY: Rich

HOLE: RI07-18

Easting	Northing	Elev.	Depth (m)
443348	7358592	597	94.49

Contractor: North Star
Drill: MD-002

SURVEY							
Depth (m)	Azimuth	Dip	Method	Depth (m)	Azimuth	Dip	Method
collar	060°	-60°	compass				

Core size: BTW
Casing depth: 13.72 (m) out

Drilling dates: August 3 to 4, 2007

Logged by: D. MacDonald

Target: _____

SUMMARY				
From (m)	To (m)	Interval	Unit	Comments
0.00	15.24	15.24	OVB	
15.24	70.68	55.44	DME	
70.68	70.73	0.05	NiMo	
70.73	94.49	23.76	OSR	

SAMPLES

Numbers: C488351 - C488370

Total: 20
Date sent:

COMMENTS

PROPERTY: RICH **HOLE:** RI07-18

Struct. Type	Struct. Attitude	LITHOLOGY From (m)	To (m)	Interval (m)	Type	Unit	Texture	Modifier	Notes:	ALT.	MINERALS Ca	Sx	Fe	Qz	SAMPLES From (m)	To (m)	Interval (m)	Sample	Ni (ppm)	Zn (ppm)	Mo (ppm)	Blocks From (m)	To (m)	Intvl. (m)	GEOTECHNICAL REC (m)	REC Percent	RQD (m)	RQD Percent	Weathering	Hardness	JOINTS Frequency	Attitude	Shape	Roughness	Infilling
		0.00	15.24	15.24	OVB																														
BD	70	15.24	70.68	55.44	SHL	DME	LA	BK-	15.24 - 20.21 m Highly fissile, finely LA BK SHL (flat-bedded), with uncommon limonite staining on fracture surfaces and rarely on bedding planes; Sx-rich bed ~10 cm wide with abundant but cryptic calcite (fizzes intensely with HCl and yields strong H2S odour); Sx is vfg and concentrated towards end of interval.	w-f			+									15.24	18.28	3.04	1.24	41	0.00	0	SW	W	10	80	2	2	Li
																									18.28	21.35	3.07	2.30	75	0.35	11	SW	W	12	70	2	2	Li
BD	60-80				LST	DME	LA	GY	20.21 - 21.13 m Finely laminar GY silty LST that coarsens downwards and has a disrupted upper boundary and erosional basal contact (scoured and ripped up) with the underlying BK SHL.	w			+																								
BD	70				SHL	DME	LA	BK		w			+										21.35	24.38	3.03	2.74	90	0.00	0	SW	W	25	70	2	2	ALS
									21.13 - 42.84 m Interval comprises 2 coarsening downwards cycles; first cycle extends from 21.13 m to 38.70 m, the second cycle from 38.70 - 42.84 m; both cycles start with finely laminar BK-GY, flat-bedded SHL interbedded with common GY siliceous and sandy SLT, and said SLT beds become slightly thicker andmore common with depth; overall transition from BK SHL into GY SLT is moderately sharp (over 5 cm); BK SHL in 2nd coarsening cycle is slightly darker than that of the 1st cycle.													24.38	27.43	3.05	2.80	92	0.00	0	SW	MS	25	20	2	2	Qz
																							27.43	30.48	3.05	2.78	91	0.61	20	FR	MS	18	10	2	2	Li
																							30.48	33.53	3.05	1.62	53	0.00	0	FR	MS	18	70	2	2	Li
																							33.53	36.58	3.05	2.71	89	0.00	0	FR	MS	21	80	2	2	Li
																							36.58	39.62	3.04	2.49	82	0.10	3	FR	MS	21	70	2	2	Li
																							39.62	42.67	3.05	2.87	94	0.70	23	FR	MS	15	70	2	2	Li
BD	80				LST	DME	LA	GY	42.84 - 43.09 m Finely laminar, coarsening downward GY slightly sandy SLT/LST with inclind bedding and v slight X-stratification (low-angle); slightly scoured lower contact with underlying BK SHL.	w			+									42.67	45.72	3.05	2.85	93	0.91	30	FR	MS	10	70	1	1	Cb

PROPERTY: RICH **HOLE:** RI07-18

Struct. Type	Struct. Attitude	LITHOLOGY From (m)	LITHOLOGY To (m)	LITHOLOGY Interval (m)	LITHOLOGY Type	LITHOLOGY Unit	LITHOLOGY Texture	LITHOLOGY Modifier	Notes:	ALT.			MINERALS Ca	MINERALS Sx	MINERALS Fe	MINERALS Qz	SAMPLES From (m)	SAMPLES To (m)	SAMPLES Interval (m)	SAMPLES Sample	SAMPLES Ni (ppm)	SAMPLES Zn (ppm)	SAMPLES Mo (ppm)	Blocks From (m)	Blocks To (m)	Blocks Intvl. (m)	GEOTECHNICAL REC (m)	GEOTECHNICAL REC Percent	GEOTECHNICAL RQD (m)	GEOTECHNICAL RQD Percent	GEOTECHNICAL Weathering	GEOTECHNICAL Hardness	JOINTS Frequency	JOINTS Attitude	JOINTS Shape	JOINTS Roughness	JOINTS Infilling
BD	80-85				SHL	DME	LA	BK	43.09 - 45.45 m Interval starts with finely laminar BK SHL and gradually coarsens to GY fg sandy SLT (slightly inclined bedding by end of interval; rare, thin (2 cm) beds of calcareous fg GY SLT/SS.	w			+																									
BD	80				SLT/L	DME	LA	GY	45.45 - 45.71 m Calcareous, fg-mg sandy GY SLT that fines downward slightly and has slightly inclined bedding and organic-rich , thin laminae (2 mm - 5 mm).	w			+																									
BD	80-85				SHL	DME	LA	BK	45.72 - 54.93 m Coarsening downwards cycle; interval starts with laminar BK SHL interbeddd with common, finely-to-coarsely laminar GY sandy SLT bds that range from 1 cm to 5 cm thick and become slightly wavy laminar near the end of the interval; GY SLT beds become slightly more abundant near end of interval; rare Sx laminae (1 - 2 mm thick)	w			+	+											45.72	48.77	3.05	2.95	97	1.47	48	FR	MS	8	70	1	1	Cb
																										48.77	51.82	3.05	2.78	91	1.43	47	FR	MS	4	70	1	1	Cb
																										51.82	54.87	3.05	3.03	99	2.32	76	FR	MS	3	30	1	1	Cb
BD	80				SHL	DME	LA	BK-	54.93 - 70.68 m Another coarsening downward cycle with same lithology and trends as in previous interval; rare Sx (Py) laminae 2 mm thick.	w			+	+																									
																										54.87	57.91	3.04	3.25	107	2.25	74	FR	MS	3	30	1	1	Cb
																										57.91	60.93	3.02	2.98	99	1.48	49	FR	MS	5	45	1	1	Cb
																										60.93	64.01	3.08	2.85	93	1.75	57	FR	MS	4	60	1	1	Cb
																	63.08	64.58	1.50	C488351	151.0	389	39.60															
																	64.58	66.08	1.50	C488352	149.5	264	42.40															
																	66.08	67.08	1.00	C488353	135.0	201	44.00	64.01	67.06	3.05	2.88	94	0.70	23	FR	MS	9	70	1	1	Cb
																	67.08	68.08	1.00	C488354	140.5	154	50.40															
																	68.08	69.08	1.00	C488355	163.5	175	56.80															
																	69.08	69.58	0.50	C488356	182.5	250	67.20															
																	69.58	70.08	0.50	C488357	148.0	421	45.00	67.06	70.10	3.04	2.98	98	1.71	56	FR	MS	5	70	1	1	Cb
																	70.08	70.38	0.30	C488358	164.0	518	46.30															
																	70.38	70.68	0.30	C488359	189.0	461	44.50															
BD	var	70.68	70.73	0.05	SX	NIMO	LA/E	BZ	70.68 - 70.73 m Bronze, finely wavy laminar Sx bed, moderately-to-heavily bioturbated; moderate soft-sediment slumping into underlying BK SHL; some of the NIMO Horizon is lost to drilling process (irregular fractures).	w				+			70.68	70.73	0.05	C488360	4.30%	7200	1750	70.10	73.15	3.05	3.01	99	2.10	69	FR	MS	4	30	1	1	Cb
BD	80	70.73	94.49	23.76	SHL	OSR	LA	BK	70.73 - 70.99 m Finely laminar non-calcareous BK SHL (slightly inclined bedding) with sharp lower contact with LST BALL.	w-f							70.73	70.99	0.26	C488361	358.0	848	100.50															
BD	var				BAL/L	OSR	LA/E	GY	70.99 - 71.35 m LST BALL - GY slightly brecciated fg LST with v sharp upper and lower contacts with BK SHL above and below LST BALL.	w			+				70.99	71.35	0.36	C488363	20.5	60	4.51															
BD	80-85				SHL	OSR	LA	BK	71.35 - 94.49 m Finely laminar GY-BK SHL (slightly inclined-to-flat bedded from top to base) interbedded with common GY, slightly sandy SLT beds up to 20 - 30 cm thick, which beds become much less common with depth to being almost absent by the last 2 - 3 m of the interval; BK SHL becomes calcareous	w			+	+			71.35	71.85	0.50	C488364	121.5	323	38.10	73.15	76.20	3.05	2.98	98	2.28	75	FR	MS	3	40	1	1	Cb
																	71.85	72.35	0.50	C488365	103.5	161	27.90															
																	72.35	73.35	1.00	C488366	116.5	436	29.80															
																	73.35	74.35	1.00	C488367	107.0	344	31.10	76.20	79.25	3.05	3.01	99	2.10	69	FR	MS	2	25	1	1	Cb
																	74.35	75.35	1.00	C488368	106.5	290	28.80															
																	75.35	76.85	1.50	C488369	130.0	268	34.10															
																	76.85	78.35	1.50	C488370	139.5	286	37.10	79.25	82.30	3.05	2.90	95	2.00	66	FR	MS	3	25	1	1	Cb
																	BLANK			C488362	5.7	20	0.74															
																										82.30	85.34	3.04	3.05	100	1.88	62	FR	MS	3	20	1	1	Cb

PROPERTY: RICH **HOLE:** RI07-18

Struct.		LITHOLOGY								ALT.			MINERALS				SAMPLES							Blocks			GEOTECHNICAL						JOINTS					
																											REC		RQD									
Type	Attitude	From (m)	To (m)	Interval (m)	Type	Unit	Texture	Modifier	Notes:				Ca	Sx	Fe	Qz	From (m)	To (m)	Interval (m)	Sample	Ni (ppm)	Zn (ppm)	Mo (ppm)	From (m)	To (m)	Intvl. (m)	(m)	Percent	(m)	Percent	Weathering	Hardness	Frequency	Attitude	Shape	Roughness	Infilling	
									the interval, BK SHL becomes calcareous from 73.02 m until EOH; recrystallization textures appear in BK SHL at ~72 m onwards; BK SHL darkens slightly with depth and is harder then the BK SHLs in the DME, above; common Sx (Py) blebs and bands parallel to bedding from 1 - 1.5 cm thick; intervals fines downward in general.																														
																								85.34	88.39	3.05	3.09	101	2.93	96	FR	MS	1	30	1	1	Cb	
																								88.39	91.44	3.05	3.11	102	2.58	85	FR	MS	1	30	1	1	Cb	
																								91.44	94.49	3.05	2.32	76	0.21	7	FR	MS	10	70	1	1	Cb	
		94.49							END OF HOLE																													

NiMo PROJECT

PROPERTY: Rich

HOLE: RI07-19

Easting	Northing	Elev.	Depth (m)
443216	7358794		94.49

Contractor: North Star
Drill: MD-002

SURVEY							
Depth (m)	Azimuth	Dip	Method	Depth (m)	Azimuth	Dip	Method
collar	060°	-75°	compass				

Core size: BTW
Casing depth: 30.48 (m) out

Drilling dates: August 4 to 8, 2007

Logged by: D. MacDonald

Target: _____

SUMMARY				
From (m)	To (m)	Interval	Unit	Comments
0.00	20.00	20.00	OVB	
20.00	80.59	60.59	DME	
80.59	80.62	0.03	NiMo	
80.62	94.49	13.87	OSR	

SAMPLES

Numbers: C488391 - C488402

Total: 12
Date sent: August 27, 2007

COMMENTS

PROPERTY: RICH **HOLE:** RI07-19

Struct. Type	Struct. Attitude	LITHOLOGY From (m)	LITHOLOGY To (m)	LITHOLOGY Interval (m)	LITHOLOGY Type	LITHOLOGY Unit	LITHOLOGY Texture	LITHOLOGY Modifier	Notes:	ALT.			MINERALS Ca	MINERALS Sx	MINERALS Fe	MINERALS Qz	SAMPLES From (m)	SAMPLES To (m)	SAMPLES Interval (m)	SAMPLES Sample	SAMPLES Ni (ppm)	SAMPLES Zn (ppm)	SAMPLES Mo (ppm)	Blocks From (m)	Blocks To (m)	Blocks Intvl. (m)	GEOTECHNICAL REC (m)	GEOTECHNICAL REC Percent	GEOTECHNICAL RQD (m)	GEOTECHNICAL RQD Percent	GEOTECHNICAL Weathering	GEOTECHNICAL Hardness	JOINTS Frequency	JOINTS Attitude	JOINTS Shape	JOINTS Roughness	JOINTS Infilling
		0.00	20.00	20.00	OVB				0 - 20.00 m Overburden																												
BD	80	20.00	80.59	60.59	SHL	DME	LA	BK	20.00 - 33.40 m Highly fissile and moderately friable GY-BK, flat-bedded SHL, fair-to-moderate alteration (clay) and common limonite staining on fracture surfaces; degree of weathering decreases with depth; uncommon, thin beds (2 - 4 cm) of flat-bedded, GY siliceous SLT. Rare, thin quartz veinlets.	f-m					+	+									20.00	24.38	4.38	0.65	15	0.00	0	SW	MS	20	60	3	3	Li
																										24.38	27.43	3.05	0.57	19	0.00	0	SW	MS	20	60	2	2	Li
																										27.43	30.48	3.05	1.89	62	0.00	0	SW	MS	20	50	2	2	Li
																										30.48	33.53	3.05	2.15	70	0.00	0	SW	MS	20	50	1	2	Qz
BD	75				SHL	DME	LA/F	BK	33.40 - 39.70 m Same BK SHL as in previous interval (slightly more finely laminar than above), except fractures parallel to bedding become abundant, and BK SHL becomes darker and slightly less competent with depth; rare, thin quartz veinlets (1 mm wide) both parallel and at high angles to bedding.	f						+									33.53	36.58	3.05	1.75	57	0.00	0	SW	MS	20	60	1	2	Qz
																										36.58	39.62	3.04	0.55	18	0.00	0	SW	MS	20	80	1	2	Qz
BD	75				SHL	DME	LA	BK	39.70 - 43.24 m Finely laminar BK SHL as above, becoming more earthy in texture (softer, higher clay content), and slightly more weathered; SHL has a corroded appearance (voids, mostly connected parallel to BD) in last ~1 m of the interval; less competent and more friable than above SHLs; v. rare Sx-flecks and lenses.	w-f				+											39.62	42.67	3.05	2.28	75	0.00	0	SW	MS	20	80	1	2	Qz

PROPERTY: RICH **HOLE:** RI07-19

Struct. Type	Struct. Attitude	LITHOLOGY From (m)	LITHOLOGY To (m)	LITHOLOGY Interval (m)	LITHOLOGY Type	LITHOLOGY Unit	LITHOLOGY Texture	LITHOLOGY Modifier	Notes:	ALT.	MINERALS Ca	MINERALS Sx	MINERALS Fe	MINERALS Qz	SAMPLES From (m)	SAMPLES To (m)	SAMPLES Interval (m)	SAMPLES Sample	SAMPLES Ni (ppm)	SAMPLES Zn (ppm)	SAMPLES Mo (ppm)	Blocks From (m)	Blocks To (m)	Blocks Intvl. (m)	GEOTECHNICAL REC (m)	GEOTECHNICAL REC Percent	GEOTECHNICAL RQD (m)	GEOTECHNICAL RQD Percent	GEOTECHNICAL Weathering	GEOTECHNICAL Hardness	JOINTS Frequency	JOINTS Attitude	JOINTS Shape	JOINTS Roughness	JOINTS Infilling
																						42.67	45.72	3.05	2.78	91	0.00	0	FR	MS	20	70	1	2	Qz
BD	75-80				SHL	DME	LA	BK		w	+	+																							
									43.24 - 53.80 m Finely laminar BK SHL, mostly flatly-bedded, interbedded with common GY slightly vfg sandy SLT (beds up to ~8cm thick), and with rare calcareous, GY SLT beds (2 - 5 cm thick), v rare Sx flecks and lenses												45.72	48.77	3.05	2.63	86	0.57	19	FR	MS	10	80	1	2	Qz
																						48.77	51.82	3.05	3.00	98	1.12	37	FR	MS	9	80	1	2	Cb
																						51.82	54.87	3.05	3.04	100	0.71	23	FR	MS	9	70	1	2	Cb
BX	var				SHL	DME	BX	BK	53.80 - 56.24 m Highly brecciated BK SHL v angular BK SHL clasts from 2 mm x 2 mm up to 5 cm x 2 cm, floating in a calcite matrix (up to ~ 5cm wide).	w		+											54.87	57.91	3.04	2.60	86	0.55	18	FR	MS	7	70	1	2	Cb
BD	70				SHL	DME	LA	BK		w		+										57.91	60.93	3.02	3.04	101	0.39	13	FR	MS	12	70	1	2	Cb
									56.24 - 80.59 m Finely laminar BK SHL interbedded with common GY slightly sandy (fg) SLT beds up to ~10 cm thick; generally fining downwards trend over whole interval, and GY SLT beds decrease slightly in abundance with depth; rare, high-angle calcite veinlets up to ~2mm wide.												60.93	64.01	3.08	2.32	75	0.32	10	FR	MS	13	70	1	2	Cb
																						64.01	67.06	3.05	2.25	74	0.76	25	FR	MS	9	70	1	2	Cb
																						67.06	70.10	3.04	2.87	94	1.19	39	FR	MS	8	70	1	2	Cb
																						70.10	73.15	3.05	2.94	96	0.12	4	FR	MS	17	70	1	2	Cb
																						73.15	76.20	3.05	2.18	71	0.00	0	FR	MS	20	50	1	2	Cb
															73.88	76.20	2.32	C488391	148.5	278	44.5														
															76.20	78.09	1.89	C488392	147.5	252	46.0	76.20	79.25	3.05	2.45	80	0.00	0	FR	MS	20	50	1	2	Cb
															78.09	79.09	1.00	C488393	150.5	253	42.9														
															79.09	80.09	1.00	C488394	186.0	535	48.7														
															80.09	80.59	0.50	C488395	262.0	847	64.7	79.25	82.30	3.05	2.86	94	0.55	18	FR	MS	10	50	1	2	Cb
BD		80.59	80.62	0.03	SX	NIMO	LA	BZ	80.59 - 80.62 m Interval highly fractured, poor recovery; finely laminar BZ SX that is mildly bioturbated.	w			+		80.59	80.62	0.03	C488396	6460	2880	237															
BA	80	80.62	94.49	13.87	BAL/L	OSR	LA/B	GY	80.62 - 81.02 m Slightly brecciated LST BALL, finely laminar GY SLT with variable bedding angle.	w		+			80.62	81.02	0.40	C488397	55.3	116	8.8														
BD	80-85				SHL	OSR	LA	BK		w		+	+		81.02	82.30	1.28	C488399	130.0	392	35.3	82.30	85.34	3.04	2.93	96	1.24	41	FR	MS	4	10	1	2	Cb
									81.02 - 94.49 m (EOH) Finely laminar, flat-bedded, dark BK-GY SHL which is intermittently calcareous, interbedded with common GY calcareous SLT beds up to ~35						82.30	83.30	1.00	C488400	124.5	377	33.0														
															83.30	84.80	1.50	C488401	107.5	354	29.3														
															84.80	86.30	1.50	C488402	128.5	295	34.3	85.34	88.39	3.05	3.03	99	1.84	60	FR	MS	5	60	1	2	Cb

PROPERTY: RICH **HOLE:** RI07-19

Struct.		LITHOLOGY								ALT.			MINERALS				SAMPLES							Blocks			GEOTECHNICAL						JOINTS				
																											REC		RQD									
Type	Attitude	From (m)	To (m)	Interval (m)	Type	Unit	Texture	Modifier	Notes:				Ca	Sx	Fe	Qz	From (m)	To (m)	Interval (m)	Sample	Ni (ppm)	Zn (ppm)	Mo (ppm)	From (m)	To (m)	Intvl. (m)	(m)	Percent	(m)	Percent	Weathering	Hardness	Frequency	Attitude	Shape	Roughness	Infilling
									cm thick; uncommon Sx (Py) lenses up to ~ 2								BLANK			C488398	56.4	125	14.2														
									mm x 5 mm, oriented mostly parallel to BD.															88.39	91.44	3.05	2.34	77	0.93	30	FR	MS	3	20	1	2	Cb
									EOH																												
																								91.44	94.49	3.05	3.01	99	1.99	65	FR	MS	4	20	1	2	Cb
		94.49							END OF HOLE																												

NiMo PROJECT

PROPERTY: Rich

HOLE: RI07-20

Easting	Northing	Elev.	Depth (m)
444880	7356092	646	189.28

Contractor: North Star
Drill: MD-001

SURVEY							
Depth (m)	Azimuth	Dip	Method	Depth (m)	Azimuth	Dip	Method
collar	060°	-75°	compass				

Core size: BTW
Casing depth: 51.82 (m) out

Drilling dates: August 7 to 11, 2007

Logged by: D. MacDonald

Target: _____

SUMMARY				
From (m)	To (m)	Interval	Unit	Comments
0.00	51.30	51.30	OVB	
51.30	74.42	23.12	DME	
74.42	74.51	0.09	NiMo?	oblique TCA, 1 cm thick, not typical NiMo
74.51	178.22	103.71	OSR?	not typical OSR, DME?
178.22	189.28	11.06	OSR	

SAMPLES

Numbers: C488415 - C488436

Total: 22
Date sent: August 27, 2007

COMMENTS

NiMo horizon does not have typical appearance, greater organic content in shale, OSR underlaying NiMo does not have characteristic fizz until last 11.06 m.

PROPERTY: RICH **HOLE:** RI07-20

LITHOLOGY										ALT.			MINERALS				SAMPLES							Blocks			GEOTECHNICAL						JOINTS					
Struct.																											REC		RQD									
Type	Attitude	From (m)	To (m)	Interval (m)	Type	Unit	Texture	Modifier	Notes:				Ca	Sx	Fe	Qz	From (m)	To (m)	Interval (m)	Sample	Ni (ppm)	Zn (ppm)	Mo (ppm)	From (m)	To (m)	Intvl. (m)	(m)	Percent	(m)	Percent	Weathering	Hardness	Frequency	Attitude	Shape	Roughness	Infilling
		0.00	51.30	51.30	OVB				0 - 51.30 m Overburden - Highly friable, dark BK clay and sand, earthy odour.	m-s																											
																								51.39	51.82	0.43	0.43	100	0.00	0	SW	W	30	80	2	2	ALS
BD	65-7	51.30	74.42	23.12	SHL	DME	LA	BK	51.30 - 55.03 m Highly fissile, finely laminar BK SHL with moderate amount of fractures parallel to BD; generally poor recovery; from 53.37 m - 53.42 m, common limonite on fracture surfaces and corroded appearance; common disseminated, vfg Py grains over whole interval.	f				+	+								51.82	54.87	3.05	1.70	56	0.00	0	SW	MS	30	70	3	3	Li
																								54.87	57.91	3.04	1.62	53	0.23	8	FR	MS	30	70	3	3	ALS
BD	70				LST/S	DME	LA	GY	55.03 - 56.10 m V finely laminar GY calcareous SLT (LST) that becomes v slightly sandy at base of interval; common, vfg Py grains in interval, becoming more concentrated towards end of interval.	w-f			+	+																									
BD	70				SHL	DME	LA	BK-	(51.30 - 55.03 m), except SHL becomes slightly darker with a v slight metallic-green hue; abundance of disseminated Py increases with depth, as do isolated stringers of lenses (3 mm x 1 mm) oriented ~parallel to BD. Organic (bitumen?) content increases over last 1.5 m of interval.	w-f				+								57.91	60.93	3.02	2.72	90	0.00	0	FR	MS	20	60	3	3	ALS
																								60.93	64.01	3.08	2.56	83	0.11	4	FR	MS	20	70	3	3	ALS
																								64.01	67.06	3.05	2.86	94	0.60	20	FR	MS	20	70	2	2	ALS
BD	75-80				SHL	DME	LA	BK	65.03 - 69.43 m Finely laminar BK SHL becomes slightly more competent and less fractured than in above intervals; BD angle changes over interval to ~80 degrees tca, and is slightly finer-grained towards end of interval; rare quartz veinlets ~2 mm wide parallel to BD; common Py blebs (stringers of lenses) parallel to BD; abundant disseminated, vfg Py over whole interval.	w				+		+	66.89	68.39	1.50	C488415	98.4	171	29.30																
																	68.39	69.89	1.50	C488416	83.8	235	18.95														
																	69.89	70.89	1.00	C488417	105.0	177	36.90	67.06	70.10	3.04	2.81	92	0.92	30	FR	MS	14	70	2	2	Qz
																	70.89	71.89	1.00	C488418	94.5	193	20.20														
																	71.89	72.89	1.00	C488419	110.0	212	36.60														

PROPERTY: RICH **HOLE:** RI07-20

Struct. Type	Struct. Attitude	LITHOLOGY From (m)	To (m)	Interval (m)	Type	Unit	Texture	Modifier	Notes:	ALT.			MINERALS Ca	Sx	Fe	Qz	SAMPLES From (m)	To (m)	Interval (m)	Sample	Ni (ppm)	Zn (ppm)	Mo (ppm)	Blocks From (m)	To (m)	Intvl. (m)	GEOTECHNICAL REC (m)	REC Percent	RQD (m)	RQD Percent	Weathering	Hardness	JOINTS Frequency	Attitude	Shape	Roughness	Infilling
BD	80-60				SHL	DME	LA	BK-	69.43 - 69.56 m Same BK SHL as in previous interval, except more highly weathered to clay, and much more fractured; BD angle varies from 80 to 60 degrees; common, disseminated vfg Py grains.	f				+			72.89	73.39	0.50	C488420	138.0	224	49.20	70.10	73.15	3.05	2.95	97	0.68	22	FR	MS	13	60	2	2	ALS
BD	50-65				SHL	DME	LA	BK-	69.56 - 73.39 m Finely laminar, slightly greenish black SHL that shows ~50 degree BD angle at start of interval, to ~65 degrees at end of interval; SHL is slightly more competent than that of the previous interval, and there is only on bed of GY calcareous SLT (finely laminar) at 71.95-72.04 m; common Py lenses as above.	w			+	+			73.39	73.54	0.15	C488421	31.9	156	7.34															
																	73.54	73.82	0.28	C488423	74.2	100	22.20													
BD	50				SLT/L	DME	LA	GY	73.39 - 73.54 m Finely laminar, slightly sandy GY calcareous SLT (LST), with wavy laminae at the bottom of the interval	w			+				73.82	74.12	0.30	C488424	148.5	164	51.80	73.15	76.20	3.05	2.88	94	1.00	33	FR	MS	11	50	2	2	ALS
BD	45				SHL	DME	LA	BK-	73.54 - 74.42 m Finely laminar BK SHL with abundant Py laminae up to 1 mm thick and parallel to BD, as well as disseminated, vfg Py that increases in abundance in BK SHL beds up to 3 cm thick (I.e., graded with respect to concentration).	w				+			74.12	74.42	0.30	C488425	216.0	346	73.20															
BD	50	74.42	74.51	0.09	SX	NIMO	LA	BZ	74.42 - 74.51 m V finely laminar BZ Sx (wavy laminar) parallel to BD - 2 sets of generally parallel laminae ~4 mm thick sandwich a thin bed (~1 cm wide) of algal material (possibly an algal mat/growth bed) in a LST-rich/BK SHL-poor matrix. NIMO? layers only slightly bioturbated.	w			+	+			74.42	74.51	0.09	C488426	795.0	439	129.50															
BD	50	74.51	178.22	103.71	SHL	OSR?	LA	BK	74.51 - 75.94 m Finely laminar, non-calcareous BK SHL, interbedded with uncommon GY siliceous SLT and abundant Py blebs, and vfg, disseminated Py grains.	w				+			74.51	74.81	0.30	C488427	141.5	218	38.90	76.20	79.25	3.05	2.90	95	0.77	25	FR	MS	12	50	2	2	Qz
BD	50				SHL	OSR?	LA	BK	75.94 - 80.37 m Same BK SHL as in previous interval, except abundant quartz veinlets begin from this interval onwards, mostly parallel to BD, ranging in thickness from 1 mm - 5 mm; common Py blebs and disseminated grains, as above.	w				+		+	74.81	75.11	0.30	C488428	166.5	425	43.70															
																	75.11	75.61	0.50	C488429	125.0	481	37.60													
																	75.61	76.11	0.50	C488430	136.0	369	37.60	79.25	82.30	3.05	2.98	98	0.60	20	FR	MS	13	50	2	2	Qz
BD	60				SLT/L	OSR?	LA/I	GY	80.37 - 80.50 m Finely laminar, slightly lenticular-bedded GY calcareous SLT-fg SS bed with common, vfg Py grains	w			+	+			76.11	77.11	1.00	C488431	190.0	331	35.80															

PROPERTY: RICH **HOLE:** RI07-20

Struct. Type	Struct. Attitude	LITHOLOGY From (m)	To (m)	Interval (m)	Type	Unit	Texture	Modifier	Notes:	ALT.			MINERALS Ca	Sx	Fe	Qz	SAMPLES From (m)	To (m)	Interval (m)	Sample	Ni (ppm)	Zn (ppm)	Mo (ppm)	Blocks From (m)	To (m)	Intvl. (m)	GEOTECHNICAL REC (m)	REC Percent	RQD (m)	RQD Percent	Weathering	Hardness	JOINTS Frequency	Attitude	Shape	Roughness	Infilling
BD	50				SHL	OSR?	LA	BK	80.50 - 95.60 m BK SHL becomes slightly silty overall from this depth downwards. Finely laminar BK SHL interbedded with rare GY siliceous SLT in bottom half of interval; abundant quartz veinlets up to 1 cm wide generally parallel to BD; common zones of earthy, slightly weathered and corroded BK SHL throughout interval, up to 10 cm wide; cream coloured mineral intergrown with quartz in quartz-rich veinlets @ 83.16 m and 83.85 m; bitumen-rich zone from 84.40 - 84.50 m; thin (1 mm) wavy laminar Py bands @ 85.73 m and 88.03 m (NiMo-esque); intersected, concentrically zoned Py lenses @ 95.39 - 95.53 m.	w-f			+	+		+	77.11	78.11	1.00	C488432	144.5	413	33.40																	
																	78.11	79.11	1.00	C488433	125.5	321	41.30	82.30	85.34	3.04	2.89	95	1.01	33	FR	MS	11	50	2	2	Qz
																	79.11	80.37	1.26	C488434	149.0	265	44.00														
																	80.37	80.50	0.13	C488435	106.5	215	27.70														
																	80.50	82.00	1.50	C488436	154.5	308	54.30	85.34	88.39	3.05	2.65	87	0.59	19	FR	MS	12	50	1	1	Qz
																	BLANK			C488422	3.2	18	0.31														
																								88.39	91.44	3.05	2.87	94	0.82	27	FR	MS	11	50	1	1	Qz
																								91.44	94.49	3.05	2.15	70	0.24	8	FR	MS	13	60	1	1	Qz
																								94.49	97.54	3.05	2.05	67	0.00	0	FR	MS	15	60	1	1	Qz
BD	50				SHL	OSR?	BX	BK-	95.60 - 99.82 m Poor overall recovery in this interval; highly brecciated BK SHL with corroded, earthy texture (almost vuggy); abundant quartz veinlets support the BK SHL clasts (angular, avg 1 cm x 2 cm); Sx (Py) blebs common	f				+		+																							
																								97.54	100.58	3.04	1.03	34	0.32	11	FR	MS	16	60	1	1	Qz
BD	50				SHL	OSR?	LA	BK	99.82 - 103.70 m Same BK SHL as in previous interval, except that SHL is more competent and not brecciated. Sx (Py) blebs uncommon; quartz veinlets decrease in abundance sharply by the end of the interval (almost absent).	w				+		+																							
																								100.58	103.63	3.05	2.97	97	1.16	38	FR	MS	8	60	1	2	Qz
BD	55				SHL	OSR?	LA	BK	103.70 - 112.38 m Finely laminar BK SHL as above, but generally fining downwards slightly by end of interval. Almost no quartz veinlets.	w				+																							
																								103.63	106.68	3.05	2.98	98	0.56	18	FR	MS	11	50	1	2	Qz
																								106.68	109.73	3.05	1.91	63	0.00	0	FR	MS	20	50	1	2	Qz
																								109.73	112.78	3.05	1.62	53	0.00	0	FR	MS	20	50	1	2	Qz

PROPERTY: RICH **HOLE:** RI07-20

Struct. Type	Struct. Attitude	LITHOLOGY From (m)	LITHOLOGY To (m)	LITHOLOGY Interval (m)	LITHOLOGY Type	LITHOLOGY Unit	LITHOLOGY Texture	LITHOLOGY Modifier	Notes:	ALT.			MINERALS Ca	MINERALS Sx	MINERALS Fe	MINERALS Qz	SAMPLES From (m)	SAMPLES To (m)	SAMPLES Interval (m)	SAMPLES Sample	SAMPLES Ni (ppm)	SAMPLES Zn (ppm)	SAMPLES Mo (ppm)	Blocks From (m)	Blocks To (m)	Blocks Intvl. (m)	GEOTECHNICAL REC (m)	GEOTECHNICAL REC Percent	GEOTECHNICAL RQD (m)	GEOTECHNICAL RQD Percent	GEOTECHNICAL Weathering	GEOTECHNICAL Hardness	JOINTS Frequency	JOINTS Attitude	JOINTS Shape	JOINTS Roughness	JOINTS Infilling
					SHL	OSR?	FX	BK	112.38 - 112.78 m Poor recovery, v fractured and reduced to rubbly BK SHL; Sx (Py) both disseminated and as rare blebs.	m				+											112.78	115.83	3.05	2.24	73	0.00	0	FR	MS	15	50	1	2	Qz
BD	60				SHL	OSR?	LA	BK		w			+	+		+																						
																									115.83	118.87	3.04	2.56	84	0.00	0	FR	MS	20	50	1	2	Qz
									112.78 - 178.22 m Interval comprises several coarsening downwards packages of dominantly BK SHL (85%) beds (finely laminar) up to 2 - 3 cm thick interbedded with finely laminar, GY siliceous vfg SS - sandy SLT (15%) up to 10 - 20 cm thick; quartz veinlets are uncommon-to-rare over most of this interval (0.5 - 1.0 cm wide, parallel to BD); rare, thin (1 mm) high-angle calcite veinlets; common-to-uncommon disseminated Py and rare-to-uncommon Py lenses parallel to BD (3 mm x 2 mm); several zones of minor brecciation; a few coarsening downwards packages end with corroded BK SHL (open pores). At 148.37 m, GY SLT beds become calcareous for most of the rest of the hole.																																				
																									118.87	121.92	3.05	2.55	84	0.42	14	FR	MS	15	50	1	2	Qz
																									121.92	124.97	3.05	0.84	28	0.00	0	FR	MS	15	50	1	2	Qz
																									124.97	128.17	3.20	2.20	69	0.20	6	FR	MS	13	50	1	2	Qz
																									128.01	131.06	3.05	1.62	53	0.10	3	FR	MS	14	50	1	2	Qz
																									131.06	134.11	3.05	1.85	61	0.10	3	FR	MS	14	50	1	2	Qz
																									134.11	137.16	3.05	2.15	70	0.35	11	FR	MS	13	50	1	2	Cb
																									137.16	140.21	3.05	2.83	93	0.41	13	FR	MS	17	50	1	2	Cb
																									140.21	143.26	3.05	0.46	15	0.00	0	FR	MS	13	50	1	2	Cb
																									143.26	146.30	3.04	0.97	32	0.22	7	FR	MS	14	50	1	2	Cb
																									146.30	149.30	3.00	1.33	44	0.15	5	FR	MS	5	50	1	2	Cb
																									149.35	150.35	1.00	1.90	190	0.24	24	FR	MS	11	50	1	2	Cb
																									152.40	155.45	3.05	1.56	51	0.40	13	FR	MS	10	50	1	2	Cb
																									155.45	158.50	3.05	1.81	59	0.00	0	FR	MS	18	50	1	2	Cb
																									158.50	161.54	3.04	2.45	81	0.00	0	FR	MS	20	50	1	2	Cb
																									161.54	164.60	3.06	0.60	20	0.00	0	FR	MS	20	50	1	2	Cb

PROPERTY: RICH **HOLE:** RI07-20

Struct.		LITHOLOGY								ALT.			MINERALS				SAMPLES							Blocks			GEOTECHNICAL						JOINTS					
																											REC		RQD									
Type	Attitude	From (m)	To (m)	Interval (m)	Type	Unit	Texture	Modifier	Notes:				Ca	Sx	Fe	Qz	From (m)	To (m)	Interval (m)	Sample	Ni (ppm)	Zn (ppm)	Mo (ppm)	From (m)	To (m)	Intvl. (m)	(m)	Percent	(m)	Percent	Weathering	Hardness	Frequency	Attitude	Shape	Roughness	Infilling	
																								164.60	167.64	3.04	1.45	48	0.29	10	FR	MS	18	50	1	2	Cb	
																								167.64	170.64	3.00	1.37	46	0.00	0	FR	MS	20	50	1	2	Cb	
																								170.64	173.43	2.79	0.61	22	0.00	0	FR	MS	20	80	1	2	Cb	
																								173.74	176.78	3.04	1.53	50	0.10	3	FR	MS	20	80	1	2	Cb	
																								176.78	179.83	3.05	2.50	82	0.22	7	FR	MS	16	80	1	2	Cb	
BD	70	178.22	185.63	7.41	SHL	OSR	LA	BK	178.22 - 185.63 m Finely laminar BK SHL becomes slightly calcareous and is IB with GY fg-sandy SLT beds, which coarsen downwards; SHL is more competent than in previous interval, and becomes slightly calcareous; common Sx (Py) lenses (1 - 3 mm thick, up to 2.5 cm long, oriented parallel to BD); uncommon, thin (1 mm) calcite veinlets, mostly at high angles to BD (v much like OSR in other holes)	w			+	+													179.83	182.88	3.05	2.48	81	0.77	25	FR	MS	12	80	1	2	Cb	
																								182.88	185.93	3.05	3.05	100	0.83	27	FR	MS	9	80	1	2	Cb	
BD	50	185.63	189.28	3.65	SHL	OSR	LA	BK																185.93	188.98	3.05	2.75	90	0.70	23	FR	MS	20	80	1	2	Cb	
									185.63 - 189.28 m (EOH) Finely laminar BK SHL that is moderately fissile, similar to SHL in 112.78 - 178.22 m, with uncommon Py beds (up to 5 mm thick)(fg, wavy laminar, parallel to BD and slightly slumped) EOH														188.98	189.28	0.30	0.25	83	0.00	0	FR	MS	20	80	1	2	Cb	
		189.28							END OF HOLE																													

NiMo PROJECT

PROPERTY: Rich

HOLE: RI07-22

Easting	Northing	Elev.	Depth (m)
444818	7355475		155.45

Contractor: North Star
Drill: MD-001

SURVEY							
Depth (m)	Azimuth	Dip	Method	Depth (m)	Azimuth	Dip	Method
collar	065°	-70°	compass				

Core size: BTW
Casing depth: 53.34 (m) in

Drilling dates: August 12 - 17, 2007

Logged by: J. Lane

Target: _____

SUMMARY				
From (m)	To (m)	Interval	Unit	Comments
0	53.56	53.56	OVB	weathered DME
53.56	155.45	101.89	DME	
65.46	65.47	0.01	SX	sulphide band, similar in appearance to NiMo like band in RI07-20

SAMPLES

Numbers: C488437 - C488450

Total: 14
Date sent:

COMMENTS

casing stuck, unable to pull out

PROPERTY: RICH **HOLE:** RI07-22

Struct.		LITHOLOGY								ALT.			MINERALS				SAMPLES							Blocks			GEOTECHNICAL						JOINTS					
																											REC		RQD									
Type	Attiude	From (m)	To (m)	Interval (m)	Type	Unit	Texture	Modifier	Notes:	als			py	qz	ca		From (m)	To (m)	Interval (m)	Sample	Ni (ppm)	Zn (ppm)	Mo (ppm)	From (m)	To (m)	Intvl. (m)	(m)	Percent	(m)	Percent	Weathering	Hardness	Frequency	Attiude	Shape	Roughness	Infilling	
		0.00	53.56	53.56	SHL	DME	FG	BK	very broken up mud like at times, competent pieces of black shale are very soft - crumbling when touched lightly.																												
BD	60	53.56	60.30	6.74	SHL	DME	FG	BK	Cherty black shale containing small pyrite blebs scattered throughout the core (1-3%), the blebs generally show an elongated shape along bedding planes. Aluminosilicate is seen along fractured surfaces.	st			t												53.56	54.87	1.31	1.31	100	0.00	0	FR	S	8	70	1	2	ALS
																									54.87	57.91	3.04	2.47	81	0.00	0	FR	S	15	70	1	2	ALS
																								57.91	60.93	3.02	2.80	93	0.21	7	FR	S	12	70	1	2	ALS
																	59.56	61.10	1.54	C488437	108.0	223	39.1													
BD	70	60.30	69.82	9.52	SHL	DME	FG	BK	Pyrite blebs increase slightly in concentration (3-5%). Start to see thin layers of pyrite in the core .				m				61.10	62.60	1.50	C488438	103.0	535	19.3	60.93	64.01	3.08	2.73	89	0.56	18	FR	S	13	70	1	2	ALS
																	62.60	63.60	1.00	C488439	112.5	147	31.1													
									From 63.61-63.63, a slightly coarse grained area of medium grey horizon that pinches out at the sides and swells to a thickness of 2cm thick in the middle. NOTE: at this point- do not see much in the way of quartz or carbonate in the core.								63.60	64.64	1.04	C488440	99.9	109	34.4	64.01	67.06	3.05	2.95	97	0.47	15	FR	S	11	70	1	2	ALS
																	64.64	65.14	0.50	C488441	110.5	177	44.6													
									From 65.46- 65.47 see a 1cm thick horizon suphide rich band- somewhat granular in appearance occurring within the black shale - has somewhat irregular upper and lower contacts.				s				65.14	65.44	0.30	C488442	117.0	261	35.6															
																	65.44	65.49	0.05	C488443	227.0	1795	79.2													
									67.85- first appearance of quartz within the core. Appears within a 3-4mm thick vein running parallel to bedding. The quartz now starts to occur in the core every 30-50 cm.					t-m			65.49	65.78	0.29	C488445	143.5	161	47.0	67.06	70.10	3.04	2.73	90	0.64	21	FR	S	12	70	1	2	ALS
																	65.78	66.30	0.52	C488446	155.0	242	51.2													
		69.82	69.89	0.07	CBR	DME	FG	GY	7cm thick carbonate rich horizon in the core medium grey in colour. Has a very sharp looking upper and lower contacts. The rock itself contains very thin (<1mm) carbonate stringer vein through it.								66.30	67.34	1.04	C488447	142.5	207	45.9													
		69.89	77.30	19.59	SHL	DME	FG	BK							st		67.34	68.34	1.00	C488448	108.0	147	33.2	70.10	73.15	3.05	2.56	84	0.00	0	FR	MS	15	70	1	2	ALS
																	68.34	69.84	1.50	C488449	98.4	230	27.9													
									similar shale as above, around 71.76 begin to see small sections of carbonate breccia								69.84	71.34	1.50	C488450	110.5	338	31.1													

PROPERTY: RICH **HOLE:** RI07-22

Struct. Type	Struct. Attitude	LITHOLOGY From (m)	To (m)	Interval (m)	Type	Unit	Texture	Modifier	Notes:	ALT. als			MINERALS py	qz	ca		SAMPLES From (m)	To (m)	Interval (m)	Sample	Ni (ppm)	Zn (ppm)	Mo (ppm)	Blocks From (m)	To (m)	Intvl. (m)	GEOTECHNICAL REC (m)	REC Percent	RQD (m)	RQD Percent	Weathering	Hardness	JOINTS Frequency	Attitude	Shape	Roughness	Infilling
									to see small sections of carbonate breccia within the rock- clasts are angular and less than 1cm wide, it appears that the calcite is just flooding fractures in the rock. NOTE: around 70m the core becomes quite broken up.							BLANK			C488444	9	16	0.14	73.15	76.20	3.05	2.50	82	0.25	8	FR	MS	16	70	1	2	ALS
																									76.20	79.25	3.05	3.04	100	0.72	24	FR	MS	9	70	1	2	ALS
		77.30	78.19	0.89	CBR	DME	FG	GY	carbonate rock- medium grey in colour, very hard, contains carbonate stringer veins with in it.						m																						
		78.19	112.76	34.57	SHL	DME	FG	BK	similar shale as above, again the core is quite blocky and broken up.															79.25	82.30	3.05	2.58	85	0.00	0	FR	MS	18	70	1	2	ALS
																								82.30	85.34	3.04	2.30	76	0.12	4	FR	MS	20	70	1	2	ALS
																								85.34	88.39	3.05	2.58	85	0.23	8	FR	MS	20	70	1	2	ALS
									AT 86.00 the width and concentration in the core increases. Now we are seeing up to 1cm thick quartz veins parallel to bedding . Some of these veins show structural deformation with some shale becoming intermixed within it.																														
																								88.39	91.44	3.05	2.56	84	0.20	7	FR	MS	18	60	1	2	Qz
									Around 90m the concentration of quartz in the core decreases slightly				t										91.44	94.49	3.05	2.95	97	0.44	14	FR	MS	11	60	1	2	Qz
									93.05-93.14 carbonate rich section.						st								94.49	97.54	3.05	2.77	91	0.16	5	FR	MS	15	60	1	2	Qz
																								97.54	100.58	3.04	2.68	88	0.22	7	FR	MS	14	60	1	2	Qz
																								100.58	103.63	3.05	2.86	94	0.12	4	FR	S	16	60	1	2	Qz
									102.50- the quartz veins become much thicker- up to 4cm, Some even show evidence of crack seal veining.															103.63	106.68	3.05	2.30	75	0.49	16	FR	S	13	60	1	2	Qz
																								106.68	109.73	3.05	2.64	87	0.37	12	FR	S	14	60	1	2	Qz
																								109.73	112.78	3.05	2.57	84	0.24	8	FR	S	15	60	1	2	Qz
		112.76	122.90	10.14	SHL	DME	FG	BK	The core has become very blocky crumbly, and broken up. However the core is still very cherty. NOTE there is still only trace sulfides in the rock.				t											112.78	115.83	3.05	2.37	78	0.00	0	FR	S	17	60	1	2	Qz
																								115.83	118.87	3.04	2.35	77	0.00	0	FR	S	20	60	1	2	Qz
																								118.87	121.92	3.05	2.75	90	0.42	14	FR	S	12	60	1	2	Qz

PROPERTY: RICH **HOLE:** RI07-22

Struct. Type	Struct. Attitude	LITHOLOGY From (m)	To (m)	Interval (m)	Type	Unit	Texture	Modifier	Notes:	ALT. als			MINERALS py	qz	ca		SAMPLES From (m)	To (m)	Interval (m)	Sample	Ni (ppm)	Zn (ppm)	Mo (ppm)	Blocks From (m)	To (m)	Intvl. (m)	GEOTECHNICAL REC (m)	REC Percent	RQD (m)	RQD Percent	Weathering	Hardness	JOINTS Frequency	Attitude	Shape	Roughness	Infilling
																								121.92	124.97	3.05	2.66	87	0.85	28	FR	MS	12	60	1	2	Qz
		122.90	124.90	2.00	CBR	DME	FG	GY	Medium to light grey fine grained carbonaceous horizon containing very thin carbonate stringer veins.																												
		124.90	155.45	30.55	SHL	DME	FG	BK																124.97	128.17	3.20	2.00	63	0.20	6	FR	S	12	70	1	2	Qz
									Black cherty fine grained shale interbedded with slightly coarser grained horizons generally 1-10cm thick, the coarser horizons are medium grey in colour and have quite sharp boundaries with the shale. In some of the thicker horizons that begin to appear around 131.50 there is a visible fining up sequence. There are quartz veins and stringer veins running throughout the rock, and the whole assemblage continues until the end of the hole.												128.01	131.06	3.05	2.77	91	0.33	11	FR	S	11	60	1	2	Qz
																								131.06	134.11	3.05	2.84	93	0.50	16	FR	S	9	60	1	2	Qz
																								134.11	137.16	3.05	2.80	92	0.73	24	FR	S	7	60	1	2	Qz
																								137.16	140.21	3.05	3.05	100	0.69	23	FR	S	10	60	1	2	Qz
																								140.21	143.26	3.05	3.02	99	0.42	14	FR	S	12	60	1	2	Qz
																								143.26	146.30	3.04	3.11	102	0.51	17	FR	S	13	60	1	2	Qz
																								146.30	149.30	3.00	2.73	91	0.65	22	FR	S	10	60	1	2	Qz
																								149.35	150.35	1.00	2.77	277	0.69	69	FR	S	9	60	1	2	Qz
																								152.40	155.45	3.05	2.70	89	1.19	39	FR	S	7	60	1	2	Qz
		155.45							END OF HOLE!																												

NiMo PROJECT

PROPERTY: Rich

HOLE: RI07-23

Easting	Northing	Elev.	Depth (m)
442360	7360170		20.42

Contractor: North Star
Drill: MD-002

SURVEY							
Depth (m)	Azimuth	Dip	Method	Depth (m)	Azimuth	Dip	Method
collar	060°	-70°	compass				

Core size: BTW
Casing depth: 20.42 (m) out

Drilling dates: August 17 to 19, 2007

Logged by: J. Lane

Target: _____

SUMMARY				
From (m)	To (m)	Interval	Unit	Comments
0.00	20.42	20.42	DME	extremely rubbly and weathered

SAMPLES
Numbers:
Total: 0
Date sent:

COMMENTS
Hole encountered high water presure, unable to continue. Water seeping out of hole after casing removed, plug inserted into hole to stop flow.

PROPERTY: RICH **HOLE:** RI07-23

Struct.		LITHOLOGY								ALT.			MINERALS				SAMPLES							Blocks			GEOTECHNICAL						JOINTS				
																											REC		RQD									
Type	Attitude	From (m)	To (m)	Interval (m)	Type	Unit	Texture	Modifier	Notes:	lim	als						From (m)	To (m)	Interval (m)	Sample				From (m)	To (m)	Intvl. (m)	(m)	Percent	(m)	Percent	Weathering	Hardness	Frequency	Attitude	Shape	Roughness	Infilling
		0.00	20.42	20.42	SHL	DME			very crumbly with no core larger than 10cm in length. At 7.62m- 15cm of carbonate rock, very hard, with carbonate veins throughout it. The rest of the core is very soft and broken up with limonite alteration on many of the broken surfaces, also white aluminosilicate powder is present on many surfaces.	st	m																											

442 000 mE
444 000 mE
446 000 mE
7 362 000 mN
7 360 000 mN
7 358 000 mN
7 356 000 mN
7 354 000 mN
7 352 000 mN
Property Boundary
NORTH RICH
SOUTH RICH
Soil sample location
Silt sample location
Rock sample location
T.N.
1°09'
26°20'
Grid north
Magnetic north
Annual change decreasing 30'
SOUTHAMPTON VENTURES INC.
STRATEGIC METALS LTD.
ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
FIGURE 6
SAMPLE LOCATIONS
RICH PROPERTY
NiMo PROJECT
0 100 600 m
UTM ZONE 8W, NAD 83, 116I08
FILE: ...2007/NIMO/RICH-F_6-SAMPLES.WOR
DATE: DECEMBER 2007

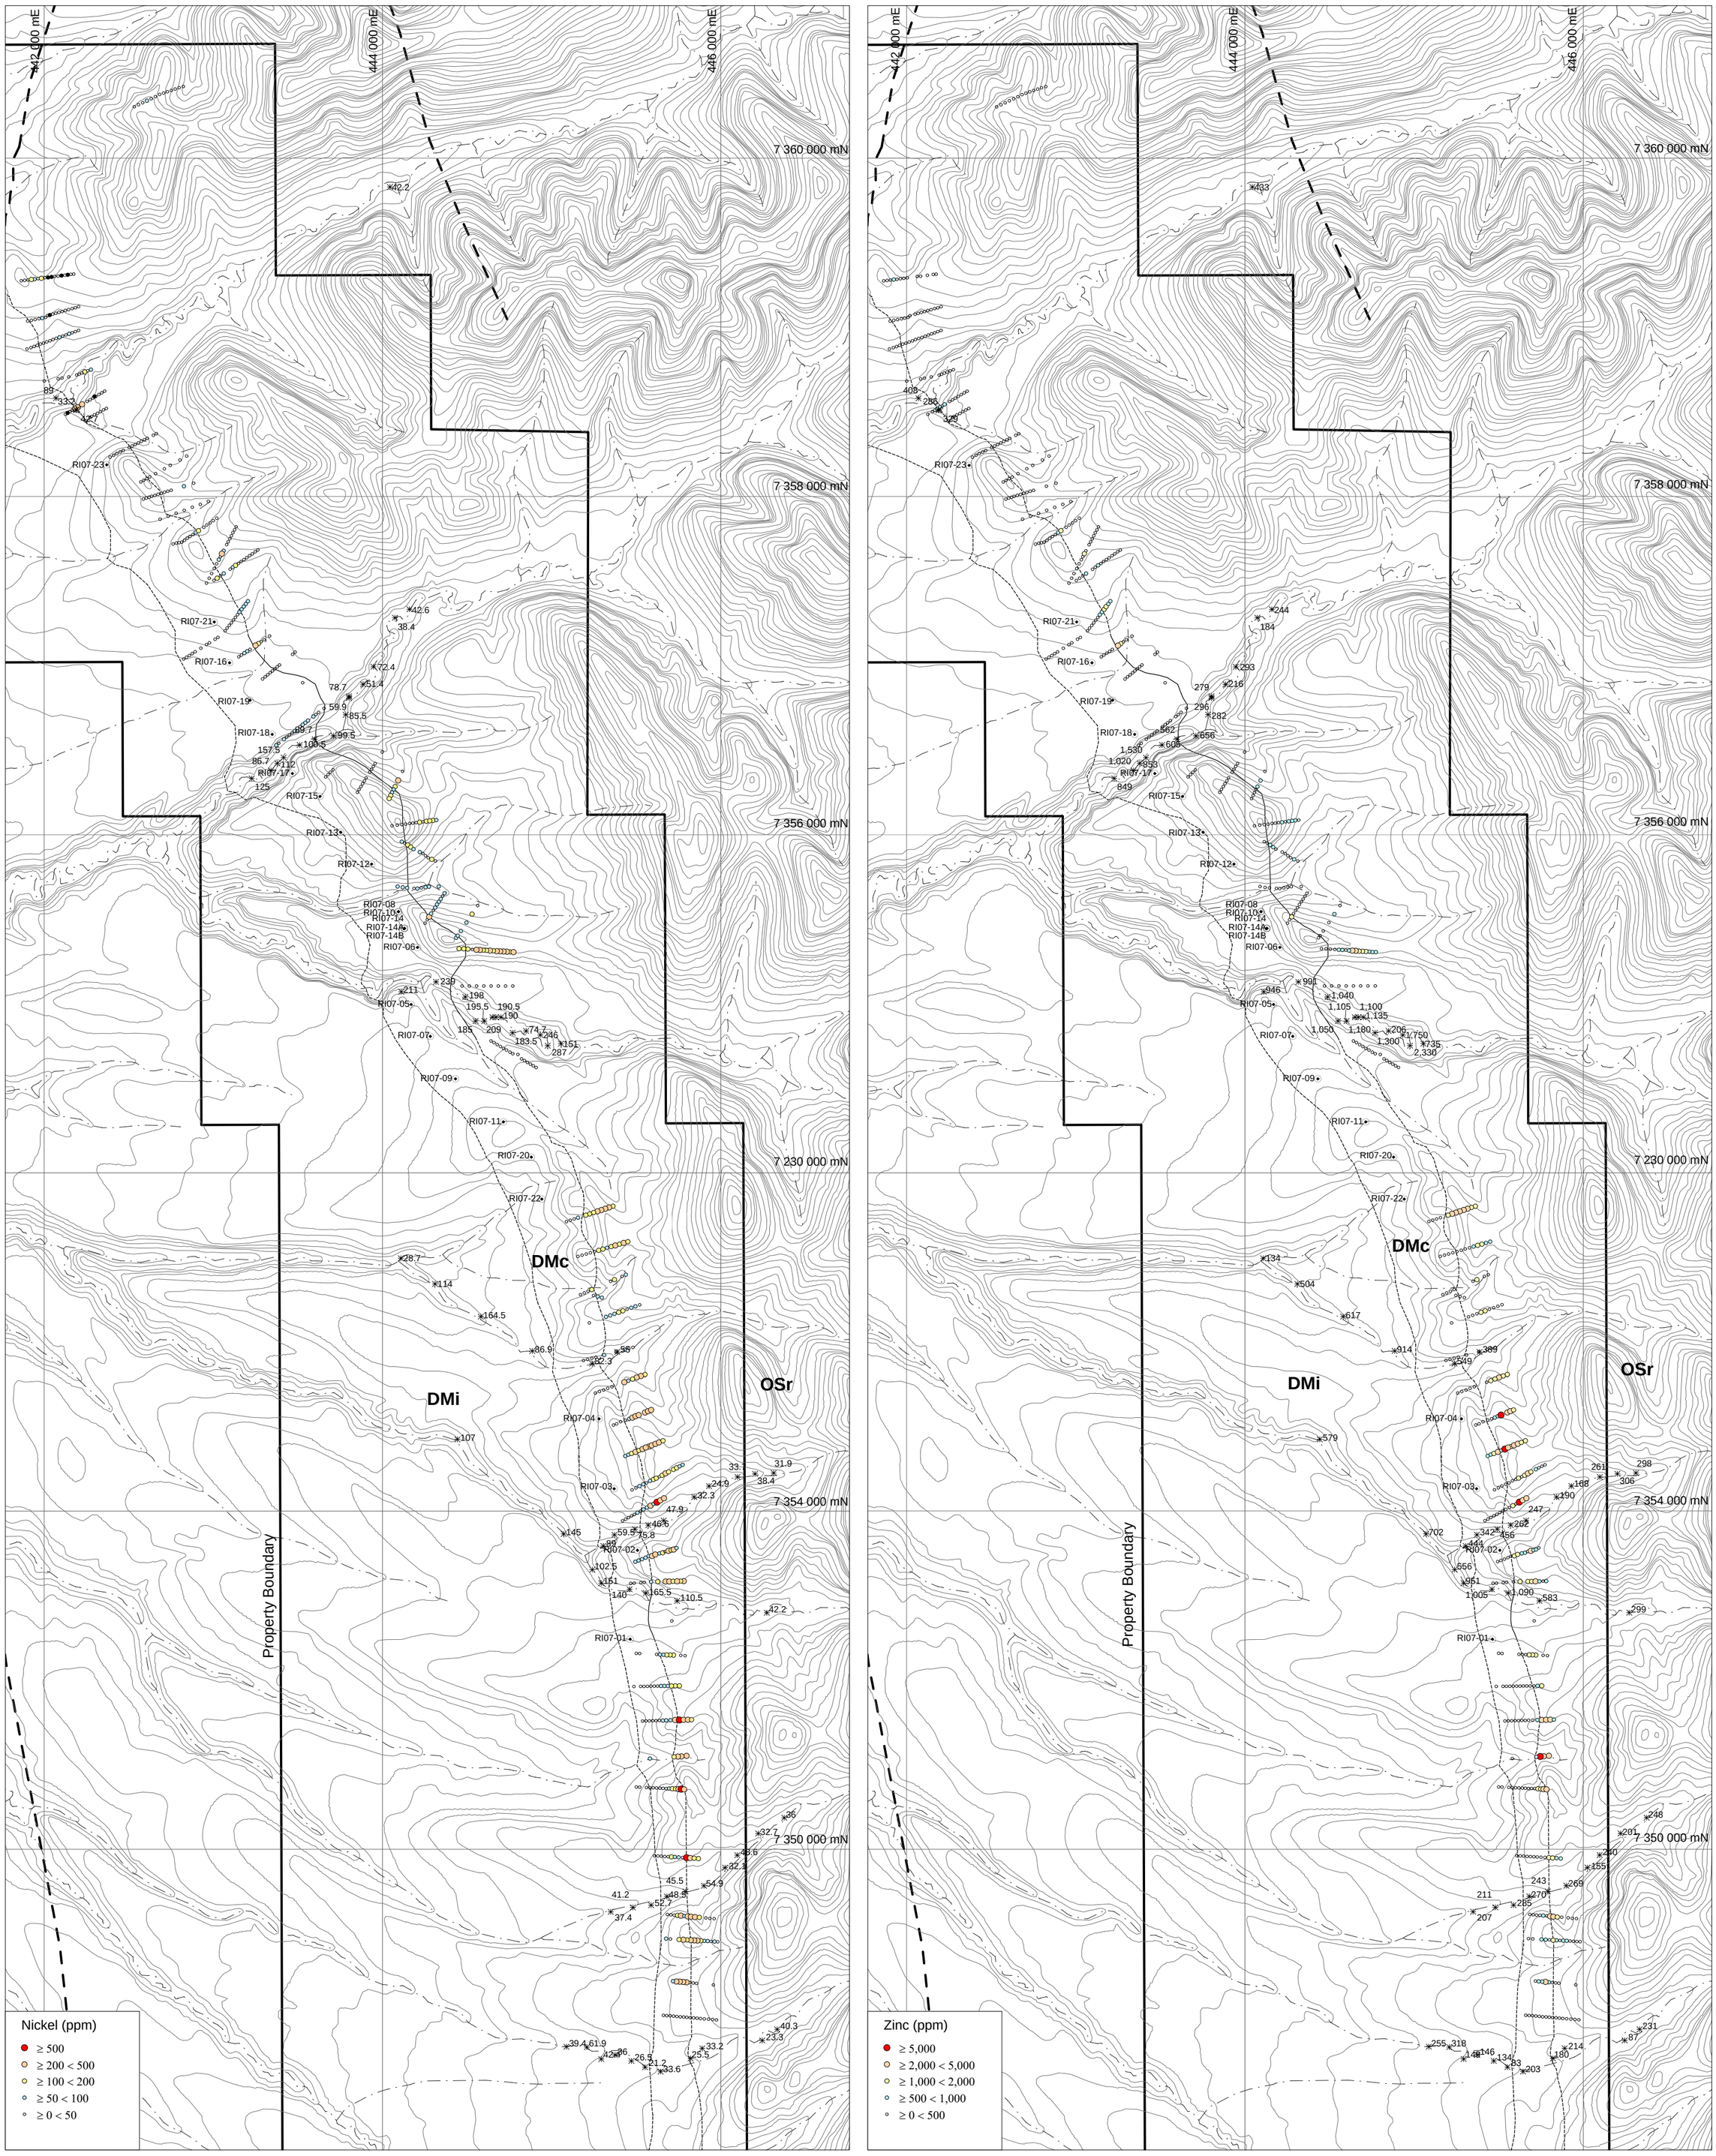

DMi Devonian Imperial Formation

DMc Devonian Canol Formation

OSr Ordovician to Silurian Road River Group

Contact (Defined, infered)

Fault

Soil sample location

222 Silt sample location (Ni or Zn value in ppm)

RI07-01 Diamond drill hole

T.N.

1°09'

26°20'

Grid north

Magnetic north

Annual change decreasing 30'

SOUTHAMPTON VENTURES INC.
STRATEGIC METALS LTD.

ARCHER, CATHRO & ASSOCIATES (1981) LIMITED

FIGURE 7

NICKEL/ZINC GEOCHEMISTRY

RICH PROPERTY

NiMo PROJECT

0 0.5 1 1.5 km

UTM ZONE 8W, NAD 83, 116I08

FILE: ...2007/NIMO/RICH-F_7-NI.WOR

DATE: DECEMBER 2007

442 000 mE
444 000 mE
446 000 mE
7 360 000 mN
7 358 000 mN
7 356 000 mN
7 230 000 mN
7 354 000 mN
7 350 000 mN
Property Boundary
DMc
DMi
OSr
RI07-01
RI07-02
RI07-03
RI07-04
RI07-05
RI07-06
RI07-07
RI07-08
RI07-09
RI07-10
RI07-11
RI07-12
RI07-13
RI07-14
RI07-14A
RI07-14B
RI07-15
RI07-16
RI07-17
RI07-18
RI07-19
RI07-20
RI07-21
RI07-22
Molybdenum (ppm)
≥ 100
≥ 50 < 100
≥ 20 < 50
≥ 10 < 20
≥ 0 < 10
Copper (ppm)
≥ 150
≥ 100 < 150
≥ 50 < 100
≥ 0 < 50
DMi Devonian Imperial Formation
DMc Devonian Canol Formation
OSr Ordovician to Silurian Road River Group
Contact (Defined, infered)
Fault
Soil sample location
222 Silt sample location (Mo or Cu value in ppm)
RI07-01 Diamond drill hole
T.N.
1°09'
26°20'
Grid north
Magnetic north
Annual change decreasing 30'
SOUTHAMPTON VENTURES INC.
STRATEGIC METALS LTD.
ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
FIGURE 8
MOLYBDENUM/COPPER GEOCHEMISTRY
RICH PROPERTY
NiMo PROJECT
0 0.5 1 1.5 km
UTM ZONE 8W, NAD 83, 116I08
FILE: ...2007/NIMO/RICH-F_8-MO.WOR
DATE: DECEMBER 2007

2000923

ARCHER, CATHRO & ASSOCIATES (1981) LIMITED
1016 – 510 West Hastings Street
Vancouver, B.C. V6B 1L8
Telephone: 604-688-2568 Fax: 604-688-2578

AFFIDAVIT

I, Joan Mariacher, of Vancouver, B.C. make oath and say:

That to the best of my knowledge the attached Statement of Expenditures for exploration work on Rich 1-186 mineral claims on Claim Sheet 116/8 is accurate.

Joan Mariacher

Sworn before me at Vancouver, B.C.

this 6th day of November, 2007.

Notary Public, Yukon Territory

Statement of Expenditures
Rich 1-186 Mineral Tenures
November 1, 2007

Contract Diamond Drilling

North Star Drilling Services Inc. $ 567,250.36

Total Footage – 2485.98 m = $228.18/m

Grant Number	Claim	Hole #	Depth (m)	Cost	Total Cost
YC45138	Rich 1	1	60.96		$13,909.85
YC45140	Rich 3	2	176.79		40,339.94
YC45142	Rich 5	3	24.38		5,563.03
YC45144	Rich 7	4	48.77		11,128.34
YC45155	Rich 18	22	155.45		35,470.58
YC45156	Rich 19	11	42.67		9,736.44
YC45157	Rich 20	20	189.28		43,189.91
YC45158	Rich 21	7	170.69		38,948.04
YC45159	Rich 22	9	39.62		9,040.49
YC45160	Rich 23	5	201.18		45,902.97
YC45162	Rich 25	6	128.02	29,211.60	
YC45162	Rich 25	8	137.16	31,297.17	
YC45162	Rich 25	10	82.30	18,779.21	
YC45162	Rich 25	14	231.65	52,859.63	132,147.61
YC45164	Rich 27	12	94.49		21,560.73
YC45166	Rich 29	15	124.97	28,515.65	
YC45166	Rich 29	17	121.92	27,819.71	56,335.36
YC45175	Rich 38	21	19.81		4,520.25
YC45469	Rich 130	13	103.63		23,646.29
YC45471	Rich 132	18	94.49		21,560.73
YC45473	Rich 134	16	121.92	27,819.71	
YC45473	Rich 134	19	94.49	21,560.73	49,380.44
YC45477	Rich 138	23	21.34		4,869.36
			2485.98		$567,250.36

North Star Drilling Services Inc.

INVOICE

Ste 276, 5158-48th Ave
Delta, B.C. V4K 5B6
Phone (604) 218-0153 Fax (604) 952-0143

DATE: August 13, 2007
INVOICE # 47-108
Drill MD 01

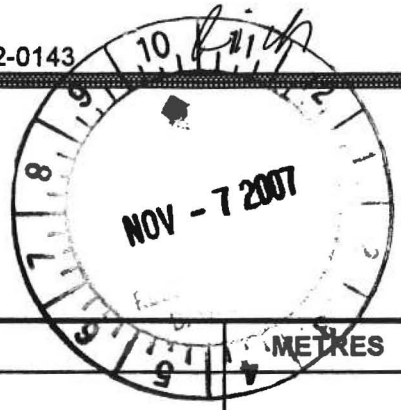

Bill To:
NiMo Project
Archer Cathro & Associates (1981) Limited
1016 - 510 West Hastings Street
Vancouver, B.C. V6B 1L8

For: Drilling Services NIMO Project

Period: July 16 - 31/07

DRILLING SERVICES	METRES	RATE	AMOUNT
BTW CORING	544.07	94.00	51,142.58
FIELD COST CHARGES	**MAN HRS**	**RATE**	**AMOUNT**
Man hours - as per attached summary	234	65.00	15,210.00
Man and machines hours - as per attached summary	195	230.00	44,850.00
MATERIALS CONSUMED	**UNIT**	**RATE**	**AMOUNT**
Extreme Gold - polymer	9	205.00	1,845.00
Extreme Blue - polymer	9	205.00	1,845.00
Geo 500 Polymer	13	210.00	2,730.00
Linseed soap	15	105.00	1,575.00
Bentonite	49	17.50	857.50
BTW Locking & adapter coupling	1	293.60	293.60
BTW 10' outer tube	1	289.80	289.80
BW 5' Casing	24	156.55	3,757.20
BTW 10' Drill Rod	1	170.10	170.10
BTW Core bits	8.5	470.40	3,998.40
BW casing shoe Heavy Duty	9	260.00	2,340.00
NW Casing shoe		290.00	
BTW Reaming Shells	3	265.85	797.55
TOTAL CONSUMABLES			$ 20,499.15
MISCELLANEOUS	**UNIT**	**RATE**	**AMOUNT**

SUBTOTAL	131,701.73
G.S.T. No. 863550935	$ 7,902.10
Less 25% of invoice (advance repayment)	32,925.43
TOTAL	$ 106,678.40

Please make cheques payable to North Star Drilling Services Inc., and mail to above address
TERMS: *Net 10 days from receipt of invoice. Overdue amounts will be charged at 2% per month*

OK'd by Mark 8 Aug 14, 2007

NORTH STAR I IG SERVICES INC.

PERIOD SUMMA... Re: Invoice 47-108

PERIOD - July 16-31 / 07

Drill MD-01			FOOTAGE DRILLED				HRLY CHGES-MEN				Total	MEN & MACH HRS			Total											COMMENTS
DATE	SHFT	Hole #	From	To	Total	Size	#men	Mve	Travel	Stdby	m/hrs	Dly	Stab	Ream	m/m hrs	Lk cpl	O.T.	Bent	Lin sp	Poly	Rod	Csg	Shoe	R/S	Bit	
July								w/line																		
16	D	RI-01	45	110	65		2		2		4		4	7	11				1	1						1 ea blue / gold
	N		110	150	40		2				0		3	5	8				1	1						
17	D		150	200	50		3	1	2		9		4	6	10								1		1	
	N		200	200	0		2				0		4	10	14											
18	D	RI-02	0	40	40	NW	3	4	2		18		2	5	7			6	2	2			1		2	
	N		40	80	40		2				0		2	8	10			16	1	1						1 ea blue / gold
19	D		80	80	0		3	6	2		24			6	6											
	N	RI-06	0	42	42		2				0		4	6	10								1	1	1	1 ea blue / gold
20	D		42	70	28	NW	2		2		4			8	8											1inner tube /
	N		70	170	100		2				0			7	7	1	1	10	1	1			1			1 x NW Casing shoe
21	D		170	300	130		2		2		4		2	5	7				1	1		16			0.5	1 ea blue / gold
	N		300	420	120		2				0		6		6											corelifters and cases
22	D		420	430	10		3	6	2		24		6		6											
	D	RI-08	0	40									9		9			8	1	1			2	1	1	1 ea blue / gold
	N		40	50	10		2				0				0											
23	D		50	210	160		2		2		4		1	3	4											
	N		210	450	240		2				0			2	2				1	1					1	1 ea blue / gold
24	D		450	450	0		2		2		4	12			12											No shifts - chopper acc.
	N		450	450	0		2				0	12			12											and no replacement
25	D	RI-10	0	80	80		3	3	2		15		2	5	7											
	N		80	240	160		2				0			4	4				2	1						1 ea blue / gold
26	D		240	270	30		3	2	2		12			3	3							8	1	1	0.5	
	N		270	270	0		2				0				0											No helicopter
27	D	RI-12	0	45	45		3	5	2		21			6	6				3	2						1 ea blue / gold
	N		45	130	85		2				0		3	4	7											
28	D		130	130	0		2	4	2		12				0											Moving/crew changing
	N		130	130	0		2				0				0											
29	D		130	140	10		2		2		4		2	2	4					1	1				0.5	
	N		140	270	130		2				0		1		1											
30	D		270	310	40		3	8	2	11	63			2	2								1			helicopter damage tower
	N		310	310	0		2				0				0											
31	D	RI-14	0	70	70		3	2	2		12		10	2	12								1			helicopter damage tower
	N		0	60	60		2				0		10												1	1 ea blue/ gld
				Feet	1785																					
TOTALS				Mtres	544.07			41	32	11	234	24	75	106	195	1	1	49	15	33	1	24	9	3	8.5	

Dly = delay
R/S - reaming shell
O.T. = Outer tube
Bent. = bentonite
Poly = polymer (GS 550)
Rd Grs = rod grease
Stab = hole stabalizing
Mve w/line = move or water

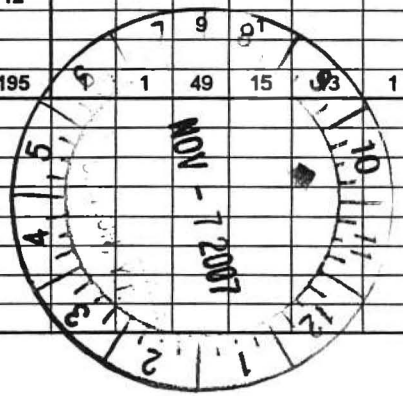

North Star Drilling Services Inc.

INVOICE

Ste 276, 5158-48th Ave
Delta, B.C. V4K 5B6
Phone (604) 218-0153 Fax (604) 952-0143

DATE: August 13, 2007
INVOICE # 47-109
Drill MD 02

Bill To:
NiMo PROJECT
Archer Cathro & Associates (1981) Limited
1016 - 510 West Hastings Street
Vancouver, B.C. V6B 1L8

For: Drilling Services NIMO Project

Period: July 16 - 31/07

DRILLING SERVICES	METRES	RATE	AMOUNT
BTW CORING	938.80	94.00	88,247.20
FIELD COST CHARGES	**MAN HRS**	**RATE**	**AMOUNT**
Man hours - as per attached summary	246	65.00	15,990.00
Man and machines hours - as per attached summary	187	230.00	43,010.00
MATERIALS CONSUMED	**UNIT**	**RATE**	**AMOUNT**
F `me Gold - polymer	8	205.00	1,640.00
ne Blue - polymer	8	205.00	1,640.00
G 550 Polymer	12	210.00	2,520.00
Linseed soap	14	105.00	1,470.00
Bentonite	142	17.50	2,485.00
BTW Locking & adapter coupling	1	293.60	293.60
BTW 10' outer tube	3	289.80	869.40
BW 5' Casing	24	156.55	3,757.20
BTW 10' Drill Rod	17	170.10	2,891.70
BTW Core bits	7.5	470.40	3,528.00
BW casing shoe Heavy Duty	1	260.00	260.00
NW Casing shoe		290.00	
BTW Reaming Shells	3	265.85	797.55
TOTAL CONSUMABLES			$ 22,152.45
MISCELLANEOUS	**UNIT**	**RATE**	**AMOUNT**
		SUBTOTAL	169,399.65
		G.S.T. No. 863550935	$ 10,163.98
		Less 25% of invoice (advance)	42,349.91
		TOTAL	$ 137,213.72

Please make cheques payable to North Star Drilling Services Inc., and mail to above address
TERMS: *Net 10 days from receipt of invoice. Overdue amounts will be charged at 2% per month*

Okd by Mark Aug 14, 2007

NORTH STAR L G SERVICES INC.

PERIOD SUMMAR Y Re: Invoice 47-109

PERIOD - July 16-31

Drill MD-02

DATE July	SHFT	Hole #	FOOTAGE DRILLED From	To	Total	Size	HRLY CHGES-MEN #men	Mve w/line	Travel	Stdby	Total m/hrs	MEN & MACH.HRS Dly	Stab	Ream	Total m/m hrs	Lk cpl	O.T.	Bent	Lin sp	Poly	Rod	Csg	Shoe	R/S	Bit	COMMENTS
16	D	RI-02	30	120	90	BTW	2		2		4		5	6	11	1	2		2	3				1	3	1 x rod grease
	N		120	280	160		2				0		6		6											
17	D		280	450	170		2		2		4		3		3											
	N		450	580	130		2				0		3	3	6											
18	D	RI-04	0	28	28		3	6	2		24		3	3	6				2	2					0.5	
	N		28	140	112		2				0		3	4	7				2	1			1			
19	D		140	160	20		2		2		4			5	5											
	D	RI-05	0	20	20		3	4			12			7				7	2	2						
	N		20	160	140		2				0		2		2											1 ea blue/gold
20	D		160	390	230		2		2		4			1	1											
	N		390	590	200		2				0		3		3											2 ea blue / gold
21	D		590	660	70		2		2		4				0											
	D	RI-07	0	20	20		3	5			15															
	N		20	90	70		2				0				0				1	1				1	1.5	
22	D	RI-07a	0	240	240		2		2		4		1	4	5		1	9	2	1						
	N		240	420	180		3				0		1	2	3											
23	D		420	560	140		2		2		4			8	8			7	1	2					1	
	N	RI-09	0	50	50		3	6			18			2	2											
24	D		50	50	0		2		2		4	12			12											Helicopter accident
	N		50	50	0		2				0	12			12											no drilling
25	D		50	70	20		2		2		4		1	10	11											
	N		70	130	60		3				0		1	7	8			20								1 Extreme blue/gold
26	D	RI-11	0	0	0		3	12	2		42				0											slow move/500D needed
	N		0	60	60		2				0		1	10	11			20								better conditions
27	D		60	140	80		3	2	2		12			10	10			16								2 ea blue / gold
	N		140	140	0		2				0				0											no move, chopper out
28	D	RI-13	0	50	50		3	8	2		30		2	6	8											
	N		50	140	90		2				0		2	6	8			18								1 ea blue/gold
29	D		140	280	140		3	2	2		12			8	8			12	1						0.5	2x inner tube ruined
	N		280	340	60		2				0		2	3	5											1 ea blue/gold
30	D	RI-15	0	100	100		3	5	2		21		2	6	8											
	N		100	270	170		2				0		2	4	6			23						1	1	150 corelifters
31	D		270	410	140		3	6	2		24			5	5											
	N		0	40	40									7	7			10	1			4				
				Feet	3080																17	20				100 Lifter cases
TOTALS				Mtres	938.80					0	246				187	1	3	142	14	12	17	24	1	3	7.5	

Dly = delay
R/S - reaming shell
O.T. = Outer tube
Bent. = bentonite
Poly = polymer (GS 550)
Rd Grs = rod grease
Stab = hole stabalizing
Mve w/line = move or water

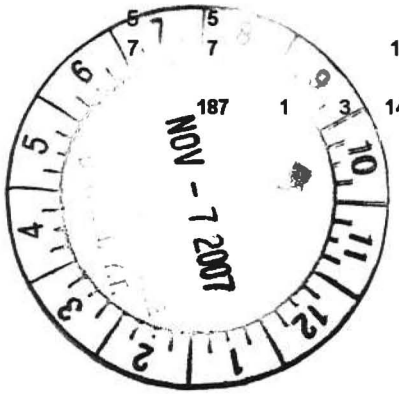

North Star Drilling Services Inc.

INVOICE

Ste 276, 5158-48th Ave
Delta, B.C. V4K 5B6
Phone (604) 218-0153 Fax (604) 952-0143

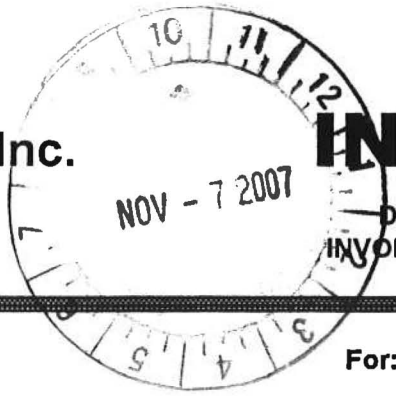

DATE: August 20/07
INVOICE # 47-110
Drill MD 01

Bill To:
NiMo Project
Archer Cathro & Associates (1981) Limited
1016 - 510 West Hastings Street
Vancouver, B.C. V6B 1L8

For: Drilling Services NIMO Project

Period: Aug 1-15/07

DRILLING SERVICES	METRES	RATE	AMOUNT
BTW CORING	541.33	108.10	58,517.77
FIELD COST CHARGES	**MAN HRS**	**RATE**	**AMOUNT**
Man hours - as per attached summary	84	65.00	5,460.00
Man and machines hours - as per attached summary	189	230.00	43,470.00
MATERIALS CONSUMED	**UNIT**	**RATE**	**AMOUNT**
Extreme Gold - polymer	3	205.00	615.00
Extreme Blue - polymer	3	205.00	615.00
GS 550 Polymer	16	210.00	3,360.00
Lin ' soap	15	105.00	1,575.00
Be a	49	17.50	857.50
BTW Locking & adapter coupling	0	293.60	
BTW 10' outer tube	0	289.80	
BW 5' Casing	4	156.55	626.20
BTW 10' Drill Rod	2	170.10	340.20
BTW Corebarrel Assy, complete	1	2,842.30	2,842.30
BTW Core bits	13	470.40	6,115.20
BW casing shoe Heavy Duty	7	260.00	1,820.00
NW Casing shoe	4	290.00	1,160.00
BTW Reaming Shells	1	265.85	265.85
2 15/16 tricone	1	1,055.85	1,055.85
TOTAL CONSUMABLES			$ 21,248.10
MISCELLANEOUS	**UNIT**	**RATE**	**AMOUNT**

SUBTOTAL	128,695.87
G.S.T. No. 863550935	$ 7,721.75
Less 25% of invoice (advance repayment)	32,173.97
TOTAL	$ 104,243.66

Please make cheques payable to North Star Drilling Services Inc., and mail to above address

TERMS: *Net 10 days from receipt of invoice. Overdue amounts will be charged at 2% per month*

ok to pay Brent D. Aug. 21, 2007

NORTH STAR [illegible]IG SERVICES INC.

PERIOD SUMM[illegible]e: Invoice 47-110

PERIOD - August [illegible]-15 / 07

Drill MD-01			FOOTAGE DRILLED					HRLY CHGES-MEN			Total	MEN & MACH.HRS			Total												COMMENTS
DATE	SHFT	Hole #	From	To	Total	Size	#men	Mve w/line	Travel	Stdby	m/hrs	Dly	Stab	Ream	m/m hrs	Lk cpl	O.T.	Bent	Lin sp	Poly	Rod	Csg	Shoe	R/S	Bit	
1	D	R1-14	60	180	120	BTW	2		1		2		2	4	6			2	1	1							
	N		180	180	0		2				0				0											No shift
2	D		180	200	20		2	1	1		4		8	2	10						2			1	1	Lost complete corebarrel
	N		200	200	0		2				0				0											No shift
3	D	R1-14A	0	180	180		2		2		4		5	12	17			5	1	2			1		1	1 ea blue / gold
	N		180	220	40		2				0				0											
4	D		220	280	60		3		2		6		6	10	16			12	1	1						
	D	R1-14B	0	35	35	BW																	1			
	N		35	110	75		2				0				0											blocky - set up sunk
5	D		110	190	80		2		2		4		6	13	19				2	2			1		3	used 16 lifters and cases
	N		190	230	40		2				0				0											Night shift stranded-fog
6	D		0	0	0		2		1		2	6			6											Fog delay 1/2 day /move
	N		0	0	0		2				0	12			12											No night shift / long shift
7	D	R1-20	0	95	95	NW	3	4	2		18			15	15			22	4	1			2xnw		1	Tough o/b - Start w NW
	D		95	115	20	BW									0								2xbw			Still no bedrock
	N		115	170	55	BW	2				0				0											
8	D		170	290	120	BTW	2		2		4			12	12				1	1					2	1 ea blue / gold
	N		290	320	30		2				0				0											NW casing take off
9	D		320	420	100		2		2		4		6	8	14				1	2					1	1 ea blue / gold
	N		420	480	60		2				0				0											
10	D		480	530	50		2		2		4		8		8				1	2					3	pulled 5 times, blocky
	N		530	570	40		2				0			6	6											ground
11	D		570	621	51		3		2		6			9	9					1		4			1	1 x NW Shoe
	N		621	621	0		2				0			12	12											Night - pull casing/rods
12	D		0	35	35	NW	3	4	2		18		9	6	15			8		1			2			1 x NW Shoe
	D		35	105	70	BW	2				0				0											
	N		105	175	70	BW	2				0				0											Still casing
13	D		175	340	165	BTW	2		2		4			6	6				2	2						
	N		340	470	130		2				0			6	6											
14	D		470	505	35		2		2		4				0				1							Day-work 1/2 shift, then
	D				0		3				0				0											crew head out on break
	N		0		0		2				0				0											
	D		0		0		3				0				0											
	N		0		0		2				0															
				Feet	1776																					
TOTALS				Mtres	541.33			9	25	0	84	18	50	121	189	0	0	49	16	16	2	4	5	1	13	

Dly = delay

R/S - reaming shell

O.T. = Outer tube

Bent. = bentonite

Poly = polymer (GS 550)

Rd Grs = rod grease

Stab = hole stabalizing

Mve w/line = move or water

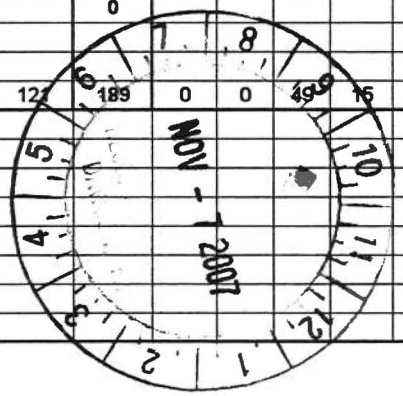

North Star Drilling Services Inc.

INVOICE

Ste 276, 5158-48th Ave
Delta, B.C. V4K 5B6
Phone (604) 218-0153 Fax (604) 952-0143

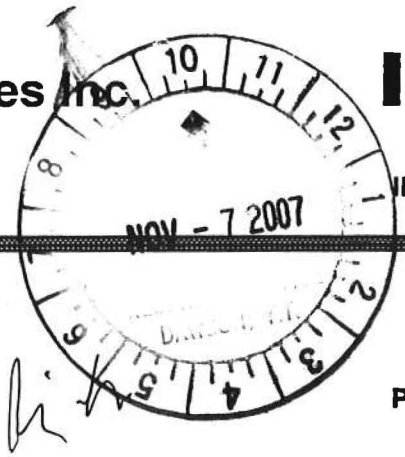

DATE: August 20/07
INVOICE # 47-111
Drill MD 02

Bill To:
NiMo PROJECT
Archer Cathro & Associates (1981) Limited
1016 - 510 West Hastings Street
Vancouver, B.C. V6B 1L8

For: Drilling Services
NIMO Project

Period: August 1-15/07

DRILLING SERVICES	METRES	RATE	AMOUNT
BTW CORING	454.16	108.10	49,094.70
FIELD COST CHARGES	**MAN HRS**	**RATE**	**AMOUNT**
Man hours - as per attached summary	181	65.00	11,765.00
Man and machines hours - as per attached summary	110	230.00	25,300.00
MATERIALS CONSUMED	**UNIT**	**RATE**	**AMOUNT**
Extr[illegible] Gold - polymer	1	205.00	205.00
Ex[illegible] Blue - polymer	1	205.00	205.00
GS [illegible] Polymer	6	210.00	1,260.00
Linseed soap	11	105.00	1,155.00
Bentonite	140	17.50	2,450.00
BTW Locking & adapter coupling	1	293.60	293.60
BTW 10' outer tube	1	289.80	289.80
BW 5' Casing	15	156.55	2,348.25
BTW 10' Drill Rod	0	170.10	
BTW Core bits	6	470.40	2,822.40
BW casing shoe Heavy Duty	4	260.00	1,040.00
NW Casing shoe		290.00	
BTW Reaming Shells	5	265.85	1,329.25
2 15/16 button Tricone - consumed in overburden	1	1,055.85	1,055.85
TOTAL CONSUMABLES			$ 14,454.15
MISCELLANEOUS	**UNIT**	**RATE**	**AMOUNT**
Manitoulin Transport charge - hauling extra casing			4,730.75
		SUBTOTAL	105,344.60
		G.S.T. No. 863550935	$ 6,320.68
		Less 25% of invoice (advance)	26,336.15
		TOTAL	$ 85,329.12

Please make cheques payable to North Star Drilling Services Inc., and mail to above address
TERMS: Net 10 days from receipt of invoice. Overdue amounts will be charged at 2% per month

OK to pay [illegible]
[illegible]

NORTH STAR DRILLING SERVICES INC.

PERIOD SUMMARY Re: Invoice 47-111

PERIOD - Aug 1-15

Drill MD-02

			FOOTAGE DRILLED					HRLY CHGES-MEN			Total	MEN & MACH.HRS			Total										COMMENTS
DATE	SHFT	Hole #	From	To	Total	Size	#men	Mve w/line	Travel	Stdby	m/hrs	Dly	Stab	Ream	m/m hrs	Lk cpl	O.T.	Bent	Lin sp	Poly	Rod	Csg	Shoe	R/S	Bit	
1	D	R1-16	40	70	30	BTW	2		2		4				0			34	1			4		2	2	Very abrasive, eating
	N		70	80	10		2				0			22	22										tooling and bits
2	D		80	260	180		2		2		4		1	10	11								1	2	1	
	N		260	400	140		2				0				0											
3	D	R1-18	0	45	45	BW	3	5	2		21		1	12	13			16	2	1		9	1			pad sunk, broke off csg
	N		45	110	65		2				0				0											
4	D		110	310	200		2		2		4		2	10	12			16	2	1						
	N	R1-19	0	45	45	BW	3	4			12				0											Pad sink, restart at 75 deg
5	D	R1-19A	0	55	55	BW	2	5			10			10	10			20								Heavy sand - triconing
	N		55	55	0		2			12	24				0											
6	D		55	55	0		2				0				0											Fog delay in morn
	N		55	70	15	BW	2				0				0			15							
7	D		70	100	30	BTW	2		2		4		6	3	9	1	1	4	2	1		2			2	tough hole / badly broken
	N		100	260	160		3				0				0											abrasive
8	D		260	260	0		2				0				0											No helper
	N		260	310	50		3		1		3			10	10			8	2	1					1	
9	D		310	310	0		2				0				0											No helper day shift
	N		0	50	50	BW	2				0				0											
	D		50		-50		2				0				0											
	N		0		0		3				0				0											
	D		0		0		3				0				0											
	N		0		0		2				0				0											
	D		0		0		3				0				0											
	N		0		0		2				0				0											
	D		0		0		3				0				0											
	N		0		0		2				0				0											
	D		0		0		3				0				0											
	N		0		0		2				0				0											
	D		0		0		3				0				0											
	N		0		0		2				0				0											
	D		0		0		3				0				0											
	N		0		0		2				0				0											
	D		0		0		3				0				0											
	N		0		40										0											
				Feet	1065																					
TOTALS				Mtres	324.62			14	11	12	86				87	1	1	113	9	4	0	15	2	4	6	

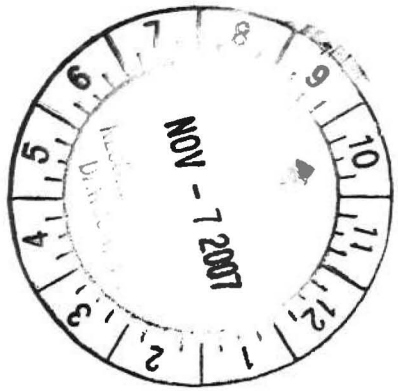

Dly = delay
R/S - reaming shell
O.T. = Outer tube
Bent. = bentonite
Poly = polymer (GS 550)
Rd Grs = rod grease
Stab = hole stabalizing
Mve w/line = move or water