

**2008 PROSPECTING and SAMPLING PROGRAM
on the GOLDEN CULVERT PROPERTY,
TUNGSTEN AREA, YUKON TERRITORY**

On Quartz Claims

| Claims | Grant Number |
|-----------------|---------------------|
| Culvert 1 | YC29100 |
| Culvert 2 | YC31957 |
| Culvert 3 | YC71979 |
| Culvert 4 – 6 | YC31958 – YC31960 |
| Culvert 7 - 8 | YC71980 – YC71981 |
| Culvert 9 – 12 | YC31961 – YC31964 |
| Culvert 13 – 16 | YC71982 – YC71985 |
| Culvert 17 - 57 | YC73335 - YC73375 |
| Culvert 58 - 70 | YC73422 - YC73434 |
| Culvert 71 | YC73863 |

Report By:

Scott Casselman B.Sc, P. Geo.
CASSELMAN GEOLOGICAL SERVICES Ltd
33 Firth Road
Whitehorse, Yukon, Y1A 4R5

For:

Gary Lee and Robert Scott
Whitehorse, Yukon

Location: 61° 57' N, 128° 25' W
NTS: 105H/16
Mining District: Watson Lake, YT
Date: December 18, 2008

TABLE OF CONTENTS

| | | |
|------|---|----|
| | Summary | 1 |
| 1.0 | Introduction..... | 2 |
| 2.0 | Location and Access | 2 |
| 3.0 | Claims | 4 |
| 4.0 | Physiography, Vegetation and Climate..... | 4 |
| 5.0 | History | 6 |
| 6.0 | Geological Setting | 7 |
| 6.1 | Regional Geological Setting..... | 7 |
| 6.2 | Property Geology | 8 |
| 7.0 | 2008 Exploration Program..... | 10 |
| 8.0 | Geochemical Analytical Procedure..... | 12 |
| 9.0 | Interpretation and Conclusions | 12 |
| 10.0 | Recommendations..... | 15 |
| 11.0 | Statement of Expenditures | 16 |
| 12.0 | References | 17 |

LIST OF FIGURES

| | | |
|----|---|---------------|
| 1 | Property Location Map | 3 |
| 2 | Claim Location Map..... | 5 |
| 3 | Regional Geology Map | 9 |
| 4 | Index Map..... | In Map Pocket |
| 5 | Stream Sediment Sample Location Map | In Map Pocket |
| 6 | Stream Sediment Sample Gold Geochemistry | In Map Pocket |
| 7 | Stream Sediment Sample Arsenic Geochemistry..... | In Map Pocket |
| 8 | Soil Sample Location Map | In Map Pocket |
| 9 | Soil Sample Gold Geochemistry..... | In Map Pocket |
| 10 | Soil Sample Arsenic Geochemistry | In Map Pocket |
| 11 | Rock Sample Location Map (West Sheet)..... | In Map Pocket |
| 12 | Rock Sample Location Map (East Sheet)..... | In Map Pocket |
| 13 | Rock Sample Location Map (North Sheet) | In Map Pocket |
| 14 | Main Showing Soil and Rock Sample Gold Geochemistry | In Map Pocket |

TABLES

| | | |
|---|-------------------------|---|
| 1 | Claim Information | 5 |
|---|-------------------------|---|

APPENDICES

| | |
|--------------|-------------------------------------|
| Appendix I | Statement of Qualifications |
| Appendix II | Rock Sample Descriptions |
| Appendix III | Geochemical Analytical Certificates |
| Appendix VI | Crew log |

SUMMARY

The Golden Culvert Property is located in the Little Hyland River Valley immediately east of the Nahanni Range Road in southeast Yukon. It is 205 km due north of the community of Watson Lake, and 10 km due west of the mining community of Tungsten, Northwest Territories. The property consists of 71 Quartz Claims that are jointly owned by Mr. Gary Lee and Mr. Robert Scott, both of Whitehorse, Yukon.

The region has a long history of exploration beginning with the discovery of the Tungsten Mine in 1954 and the initiation of production in 1962. The original, pre-production resource at the Tungsten Mine was 9 Mt with a grade of 1.42% WO_3 . The Golden Culvert Property, however does not have much of a documented history of exploration.

In 2006 and 2007 Mr Lee conducted exploration programs on the property consisting of stream sediment and soil sampling. The program resulted in the discovery of anomalous gold and arsenic in stream sediments and soils.

In 2008, Mr. Lee followed up these anomalies with a program consisting of stream sediment, soil and rock sampling, prospecting and construction of approximately 2.0 km of access trail. The program involved the collection of 15 stream sediment samples, 29 soil samples and 44 rock samples.

The results from the 2008 exploration program are very encouraging. The program located 2 source areas of gold mineralization: One, in the headwaters of the main creek draining the eastern part of the property; the second, 1.2 km to the north. Of 44 rock samples collected in 2008, 10 returned values ranging from 1.630 to 17.30 grams/tonne gold. Arsenic concentrations in these samples ranged from 27.3 to >10,000 ppm.

Recommendations for future work on the property are to expand the soil sampling program, conduct further prospecting and stream sediment sampling, geological mapping and trenching. As well, geophysical surveys such as a ground magnetic and VLF-EM survey are cost-effective and may prove helpful in tracing the mineralized veins and locating additional sources of gold. A budget for the proposed program is estimated at \$200,000.

1.0 INTRODUCTION

Mr. Gary Lee of Whitehorse, Yukon conducted an exploration program consisting of access trail construction, prospecting, soil, stream sediment and rock sampling on the Culvert claims during the summer of 2008. The work was performed during two separate visits to the property: May 31 to July 1 and August 30 to September 23. For the May 31 to July 1 portion of the program Mr. Lee and Robert Scott hired prospector Ron Stack to assist with the program. The later part of the program was performed by Mr. Lee alone. Vehicles and equipment for this program were supplied by Mr. Lee.

This report and maps were prepared by Casselman Geological Services Ltd. based on information supplied by Mr. Lee. Analytical certificates were provided directly from the laboratory in digital format. Other information used in the preparation of the report includes government publications and assessment reports in the public domain. The author is a professional geologist and has not set foot on the property.

2.0 LOCATION AND ACCESS

The Golden Culvert Property is located in the Little Hyland River Valley immediately east of the Nahanni Range Road in southeast Yukon. It is 205 km due north of the community of Watson Lake, and 10 km due west of the mining community of Tungsten, Northwest Territories. The property is centred at latitude 61° 57' N and longitude 128° 25' W (Figure 1) on NTS map sheet 105H/16.

The claims cross the Nahanni Range Road. Access to the property from Watson Lake is via the Robert Campbell Highway for 110 km, then via the Nahanni Range Road for 165 km. An access trail was cut from the Nahanni Range Road to access the eastern portion of the property. A camp location on the Nahanni Range road is 3 km north of the ATV trail in a gravel pit on the east side of the road (see Figure 3).



GARY LEE

CULVERT CLAIMS

Figure 1. Property Location Map

CASSELMAN GEOLOGICAL SERVICES Ltd

3.0 CLAIMS

The Golden Culvert Property consists of 71 Quartz Claims staked in accordance with the Yukon Quartz Mining Act in the Watson Lake Mining District (Figure 2). The mineral claim boundaries have not yet been legally surveyed. Claim data is as follows:

Table 1. Claim Information

| Claims | Grant Number | Expiry Date |
|-----------------|-------------------|-------------|
| Culvert 1 | YC29100 | 22-Jul-13 |
| Culvert 2 | YC31957 | 11-Sep-12 |
| Culvert 3 | YC71979 | 17-Sep-12 |
| Culvert 4 – 6 | YC31958 – YC31960 | 11-Sep-12 |
| Culvert 7 - 8 | YC71980 – YC71981 | 17-Sep-13 |
| Culvert 9 – 12 | YC31961 – YC31964 | 11-Sep-12 |
| Culvert 13 – 16 | YC71982 – YC71985 | 17-Sep-13 |
| Culvert 17 - 57 | YC73335 - YC73375 | 16-Jun-09 |
| Culvert 58 - 70 | YC73422 - YC73434 | 30-Jun-09 |
| Culvert 71 | YC73863 | 29-Sep-09 |




The claims are jointly owned by Mr. Gary Lee and Mr. Robert Scott of Whitehorse, Yukon. Expiry dates listed above are as listed by the Watson Lake Mining Recorder on December 18, 2008.

The land in which the mineral claims are situated is Crown Land and falls under the jurisdiction of the Yukon Government.

4.0 PHYSIOGRAPHY, VEGETATION AND CLIMATE

The property is in the Logan Mountains of eastern Yukon. The topography in the area is steep mountainous terrain with broad U-shaped river valleys. Elevations on the property range from about 1200 m to 1750 m above sea level. The lower elevations are covered with spruce and pine forest which gradually give way to barren alpine terrain. Steeper slopes are covered by talus and felsenmeer.

The area receives moderate to high precipitation of approximately 450 cm annually. Snow generally begins accumulating in the alpine areas in early September and begins receding in late April to early May. The snow is generally melted back sufficiently by late May to allow for fieldwork at lower elevations. Summer temperatures range up to 30° Celsius and winter temperatures down to -50° Celsius.

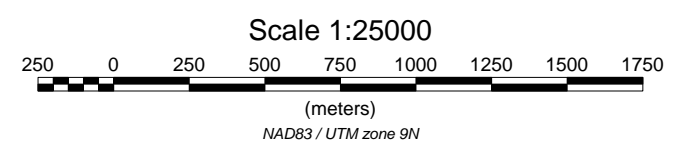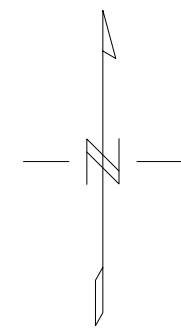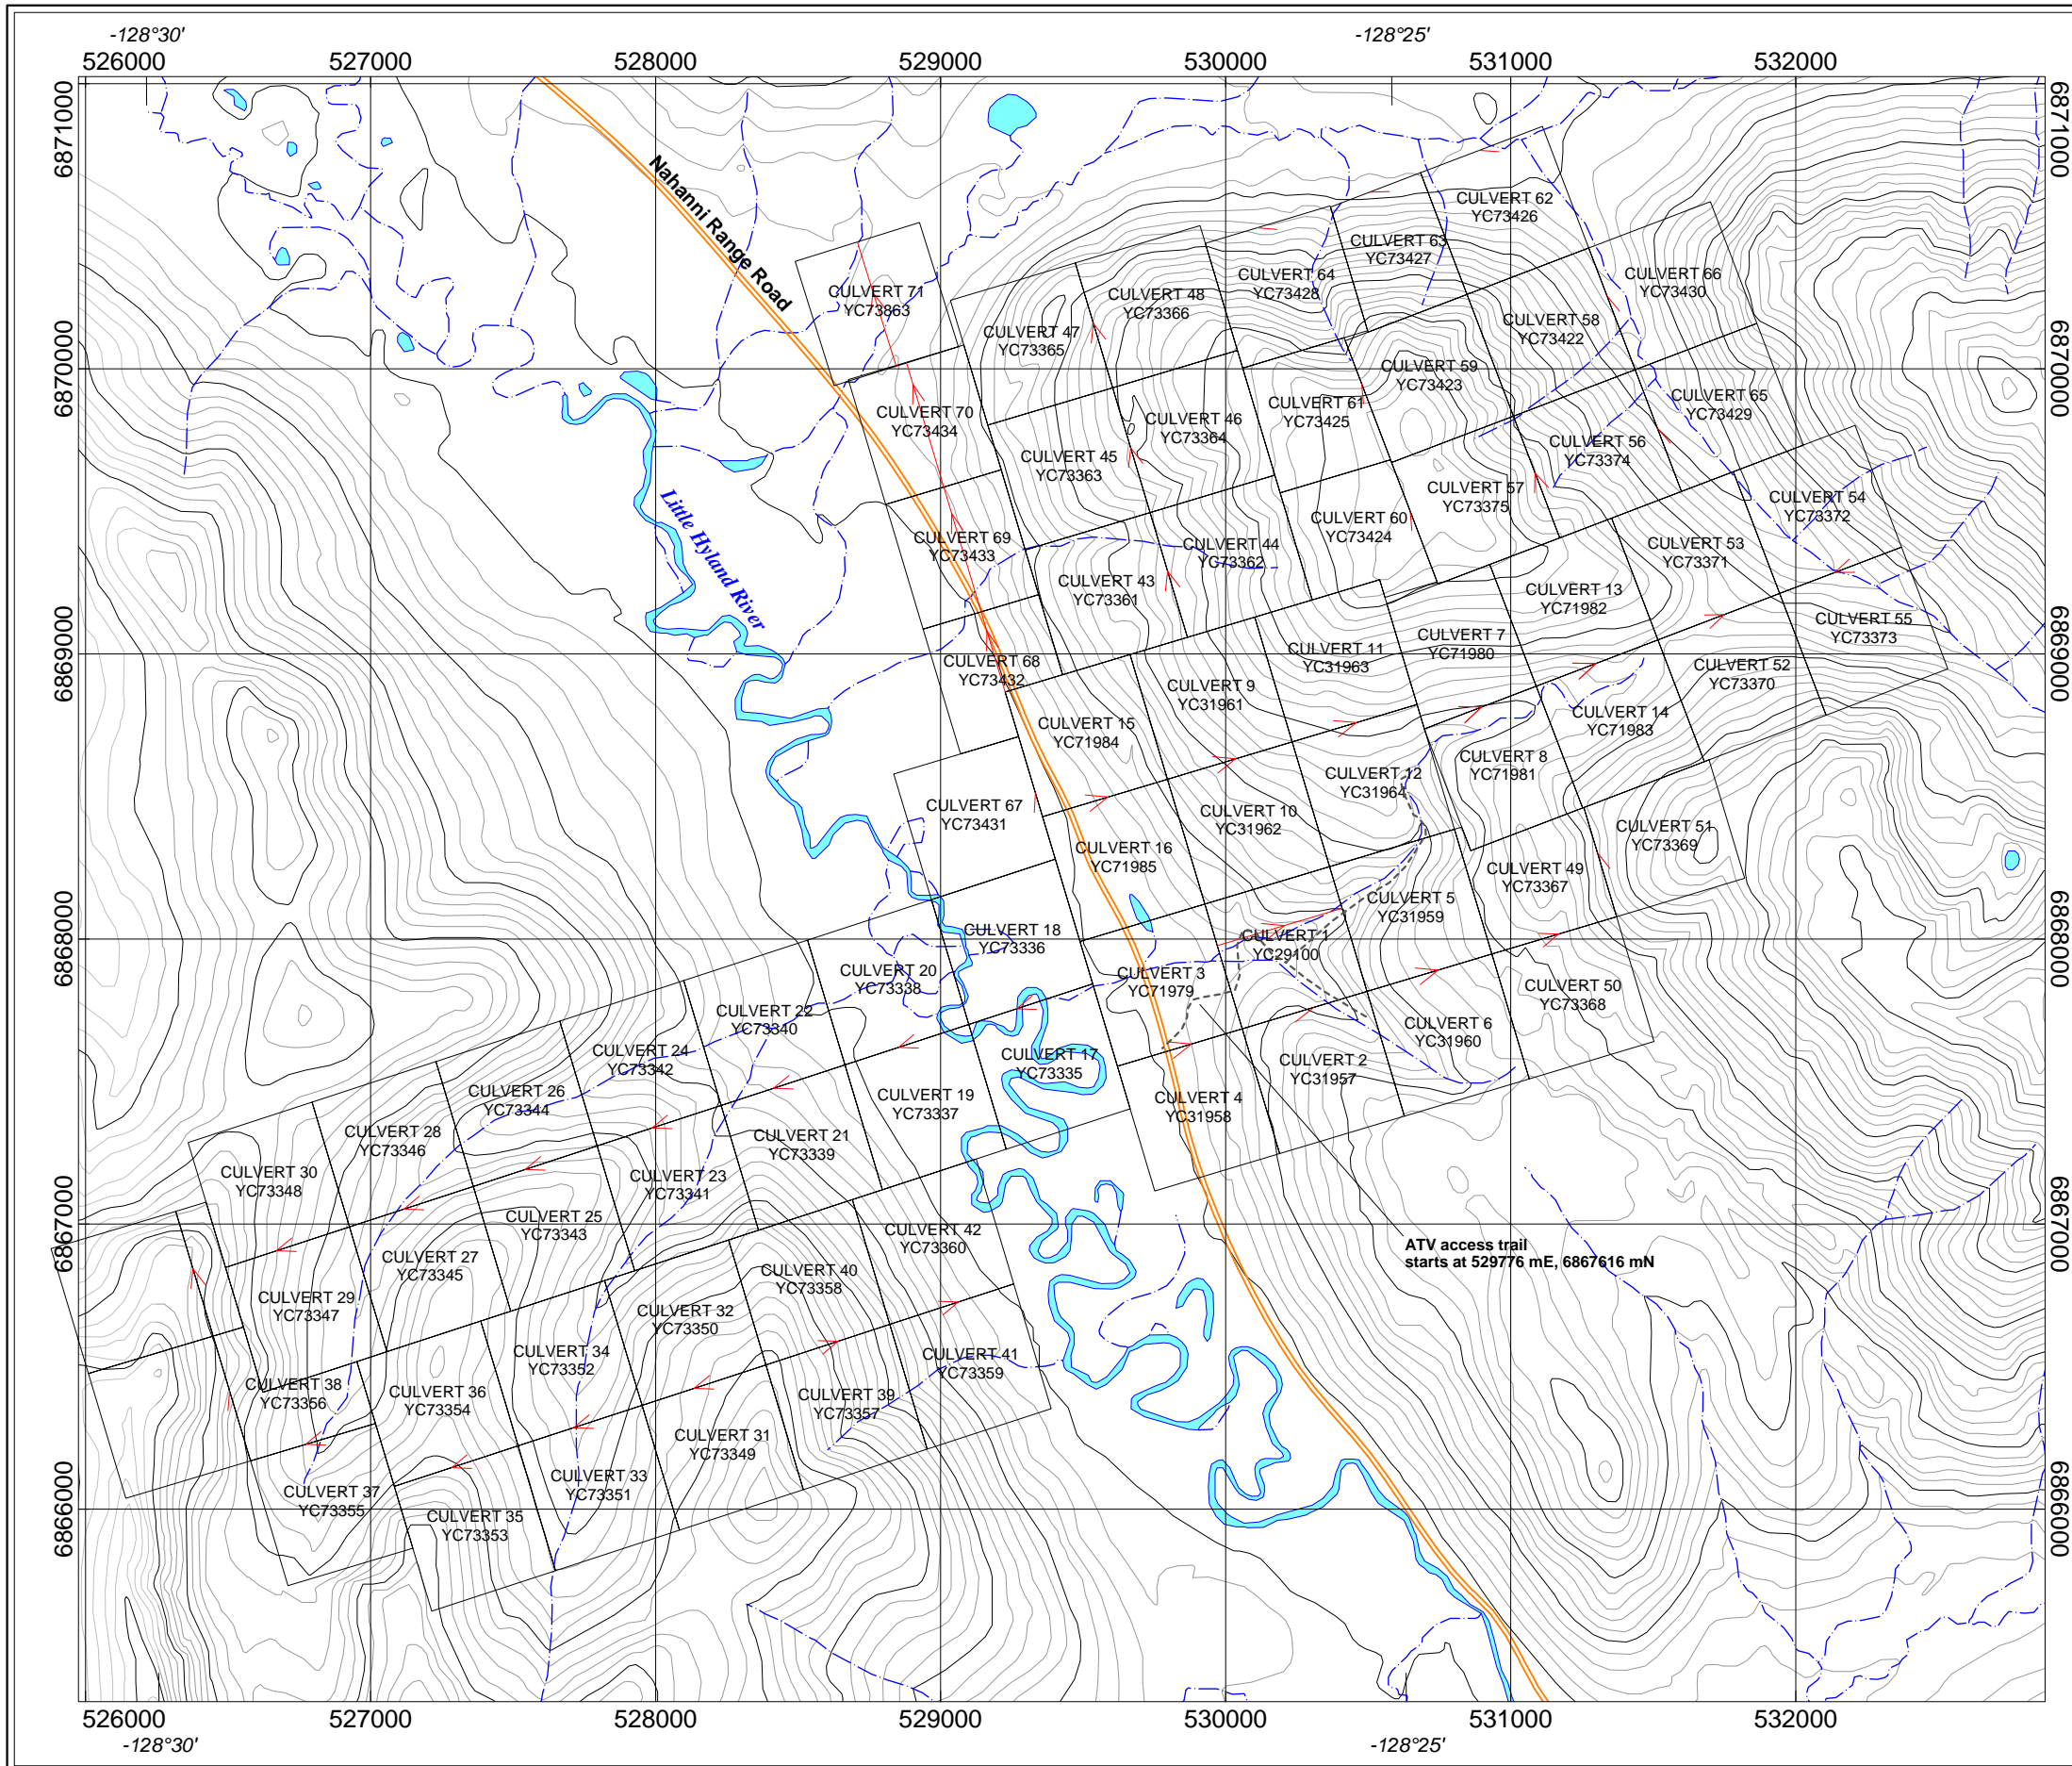

GARY LEE

**GOLDEN CULVERT PROPERTY
 CLAIM MAP**

NTS: 105H16 Mining District: Watson Lake
 DATUM: NAD83 PROJECTION: UTM, zone 9
 Date: December 16, 2008

CASSELMAN GEOLOGICAL SERVICES Ltd

ATV access trail
 starts at 529776 mE, 6867616 mN

5.0 HISTORY

The area has a long history of exploration beginning with the discovery of the Tungsten Mine in 1954 and the initiation of production in 1962. The original, pre-production resource at the Tungsten Mine was 9 Mt with a grade of 1.42% WO₃. The Golden Culvert Property, however does not have much of a documented history of exploration, prior to the activities of Mssrs. Lee and Scott.

The Yukon Minfile (DIAND, 2002) lists one mineral occurrence within 5 km of the property; the Richardo Showing. It occurs approximately 3 km south of the Culvert Property. The Yukon Minfile describes it as a ferricrete gossan that is un-mineralized and occurs within an area underlain by Cretaceous granodiorite that intrudes Cambrian slates and phyllite. The gossan was originally staked by Canada Tungsten Mining Corporation Ltd in 1961. There is no record of Canada Tungsten doing any work on the property and it was later allowed to lapse.

The property was re-staked by Mr. A. Black in 1980 as the Kay claims, then in 1981 as the Lynx claims by Mr. E. Broadhagen. In each case there is no record of work being performed on the property and the claims were allowed to lapse.

The most significant exploration activity in the area has been at the Tuna Property, located 12 km southeast of the Culvert Property. It was originally staked in 1981 by Union Carbide Exploration Ltd and has been explored for placer gold, skarn-type tungsten and lode gold. The property is underlain by a Cretaceous granodiorite stock that intrudes Cambrian slate, phyllite and siltstone of the Hyland Formation. Union Carbide performed stream sediment sampling, rock and soil sampling, geological mapping and prospecting on the property in 1982. This work identified numerous scheelite, molybdenite and chalcopyrite mineralized occurrences, often associated with quartz-tourmaline veins. However, Union Carbide later allowed the claims to lapse.

In 1989, Noranda Exploration Canada Limited, re-staked claims on the Tuna Property, but did not perform any work and these claims were later allowed to lapse. The property was later staked by Kokanee Explorations Ltd in 1991. Kokanee conducted a program of prospecting mapping and sampling in 1992. Kokanee changed its name to Consolidated Ramrod Gold Corporation later that year. In 1993, Consolidated Ramrod performed a limited amount of lithogeochemical sampling and stream sediment sampling and the program returned weak to moderately anomalous gold results.

Gold was first discovered by Robert Scott when he panned gold in the creek at the culvert on the Nahanni Range road in 1984. The first claims were staked on the Golden Culvert Property in September, 2005 and these were added on to in 2006 and 2008. In 2006 and 2007, Mr. Lee conducted exploration programs consisting of prospecting, stream sediment and soil sampling. This work returned anomalous gold and arsenic in stream sediment and soil samples. The 2008 exploration program was initiated as a follow-up to these results.

6.0 GEOLOGICAL SETTING

6.1 Regional Geological Setting

The Golden Culvert Property is located in the Selwyn Basin of eastern Yukon. The Selwyn Basin is part of the Cordilleran miogeocline and is characterized by thick accumulations of clastic sediments, with a significant component of deepwater black shales and cherts (Heon, 2007). These basinal rocks interfinger with and are bound by shallower water platformal carbonates. The Basin is bound to the north by the Dawson Fault; it grades into platformal facies to the east (Mackenzie Platform) and southwest (Cassiar Platform), may be bound by a Mesozoic thrust fault separating it from Yukon-Tanana Terrane in the Anvil district and is offset to the southwest by the Tintina Fault. The sediments range in age from Precambrian to Jurassic (Heon, 2007).

The Culvert Property area is underlain by Upper Proterozoic to Lower Cambrian dark brown weathering, thin-bedded, argillaceous fine-grained sandstone and siltstone, minor interbedded medium- to coarse grained white to light grey orthoquartzite, phyllite, slate, and argillite of the Vampire Formation (**uPCV**). West of the property, on the west side of the Nahanni Range Road are thin to thick bedded, brown to pale green shale, fine to coarse grained quartz-rich sandstone, grit, and quartz-pebble conglomerate, minor argillaceous limestone, phyllite, quartzofeldspathic and micaceous psammite, gritty psammite and minor marble of the Upper Proterozoic to Lower Cambrian Hyland Group (**PCH**) (Gordey, et. al., 2000).

Northeast of the property, in the area of the Tungsten Mine Site, occur younger sedimentary rocks of the Lower Cambrian Sekwi Formation (**ICS**), the Lower Cambrian Gull Lake Formation (**ICG**), the Upper Cambrian to Ordovician Rabbitkettle Formation (**COR**) and the Ordovician to Lower Devonian Road River Formation (**ODR**). The Sekwi Formation consists of limestone conglomerate, massive grey dolostone, medium- to thick-bedded quartz sandstone, purple siltstone and bright orange weathering, fine crystalline dolostone. The Gull Lake Formation consists of shale, siltstone and mudstone, minor quartz sandstone, rare green-grey chert, local basal limestone and limestone conglomerate, and phyllite to quartz-muscovite-biotite schist. These units are overlain by thin bedded, wavy banded, silty limestone and grey lustrous calcareous phyllite, limestone intraclast breccia and conglomerate, massive to laminated, grey quartzose siltstone and chert and rare black slate, local mafic flows, breccia, and tuff of the Rabbitkettle Formation, which is, in turn, overlain by black, gun-blue, or silvery white weathering black graptolitic shale and black chert, resistant grey weathering, thin to medium bedded, light grey to black, greenish grey or turquoise chert and minor argillaceous limestone of the Road River Formation.

This package of sedimentary rocks is intruded by resistant, blocky, fine to coarse grained equigranular to porphyritic (K-feldspar) biotite quartz monzonite and granodiorite, minor quartz diorite, minor leuco-quartz monzonite and syenite of the mid-Cretaceous Selwyn Plutonic Suite. To date there is no indication of Selwyn Suite rocks

in the immediate area of the Culvert Property; however, it is commonly believed that these intrusions drive the mineralizing fluids that introduced gold to the area.

Northwest-southeast trending faults and thrust faults dominate the structural pattern in the region.


The most significant mineralization in the area is the ore bodies of the Tungsten Mine. The ore was formed by intrusion of tungsten bearing fluids in mid Cretaceous Selwyn Suite intrusions, intruding carbonate-bearing sedimentary rocks and precipitating tungsten-rich, pyrrhotite skarns along the margins of the intrusions. The original, pre-production resource at the Tungsten Mine was 9 Mt with a grade of 1.42% WO₃.

At the Tuna Property, molybdenite, scheelite, arsenopyrite, bismuthinite, chalcopyrite, chalcocite, pyrrhotite, gold and silver are observed in quartz and quartz-tourmaline veins and in small skarn alteration zones along the margins of the Hyland Intrusion (Doherty and vanRanden, 1994).

6.2 Property Geology

The Golden Culvert Property has not been geologically mapped. According to the regional geology of the area it is underlain exclusively by sedimentary rocks of the Vampire Formation. Regional airborne magnetic survey maps show a moderate strength northwest-southeast-trending magnetic high through the property that may represent a buried intrusion. This feature could be significant for any mineralizing event at Golden Culvert.

Rock samples collected by Mr. Lee have been examined and descriptions are included in Appendix II. In general, most of the rock types observed from the sample specimens are shale, phyllite and schist. Many samples contain quartz veining and varying amounts of pyrite and occasional arsenopyrite mineralization. The pyrite mineralization is generally medium to coarse-grained, euhedral and occurs in the host rock and in quartz veins. Quartz veins are generally parallel to foliation, bull white in colour, occasionally limonite stained and occasionally vuggy after pyrite.

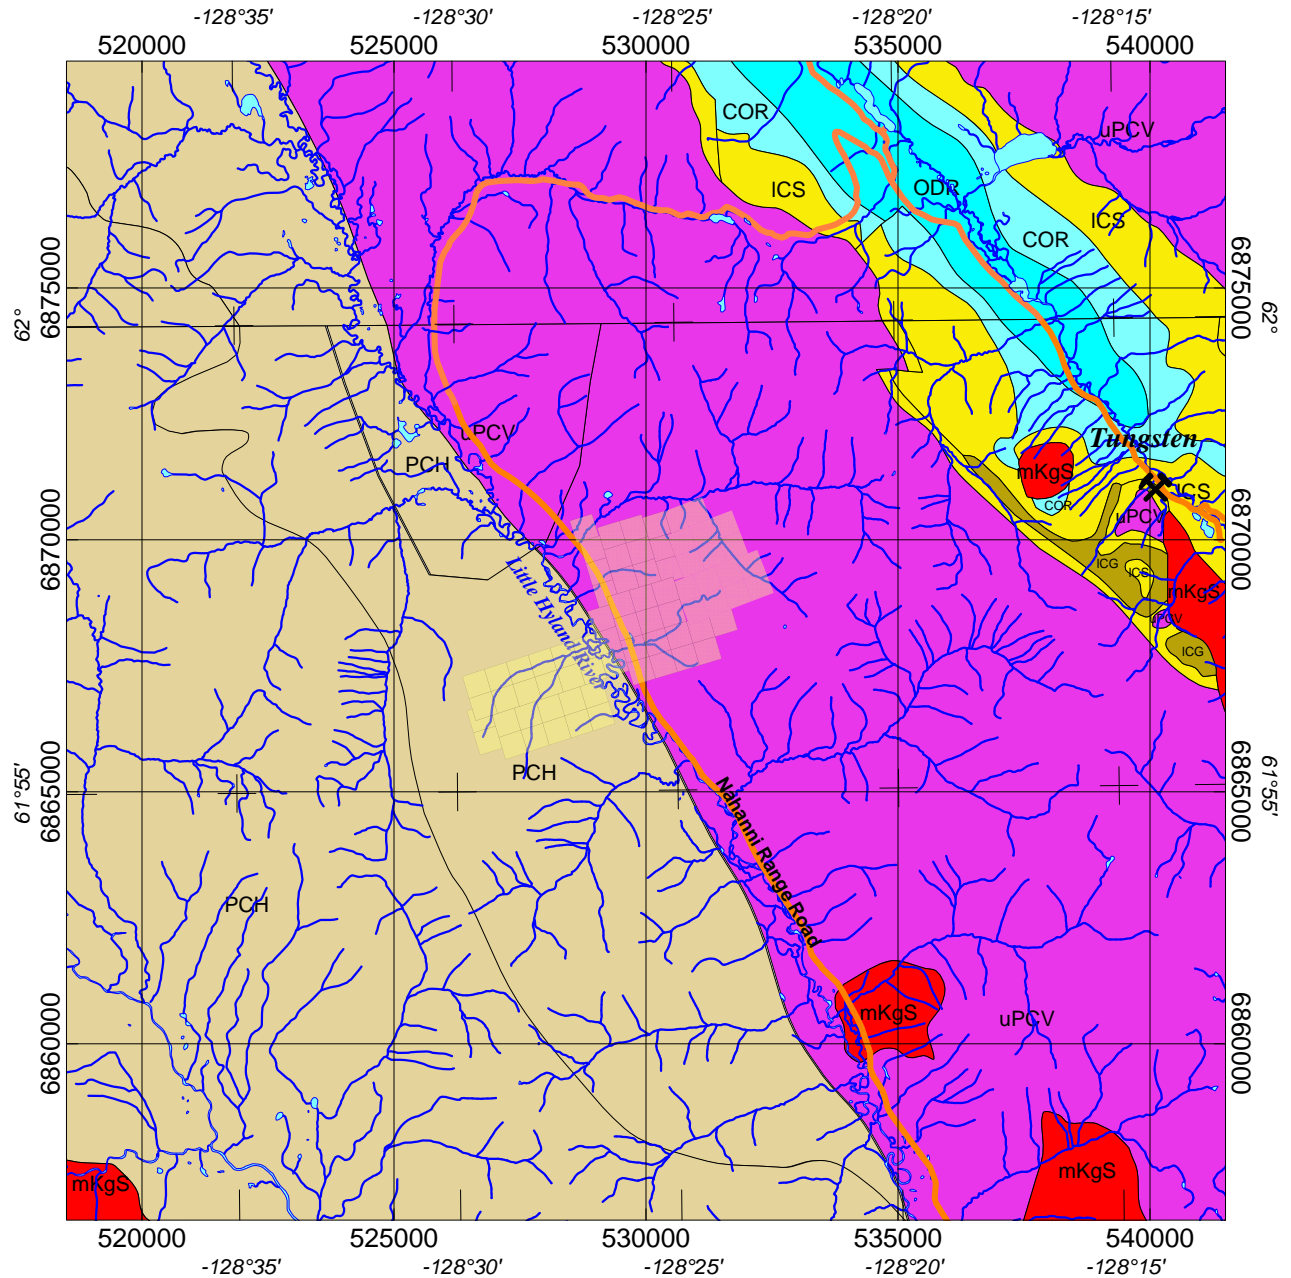

- mKgS** mid Cretaceous
Selwyn Suite - intrusives
- ODR** Ordovician to Lower Devonian
Road River Formation - sediments
- COR** Upper Cambrian to Ordovician
Rabbitkettle Formation - carbonates
- ICG** Lower Cambrian
Gull Lake Formation - sediments
- ICS** Lower Cambrian
Sekwi Formation - carbonates
- uPCV** Upper Proterozoic to Lower Cambrian
Vampire Formation - sediments
- PCH** Upper Proterozoic to Lower Cambrian
Hyland Formation - sediments

Scale 1:150000

2500 0 2500

(meters)

NAD83 / UTM zone 9N

| |
|---|
| GARY LEE |
| GOLDEN CULVERT PROPERTY Figure 3. Regional Geology Map |
| NTS: 105H16 Mining District: Watson Lake DATUM: NAD83 PROJECTION: UTM, zone 9 Date: December 16, 2008 |
| CASSELMAN GEOLOGICAL SERVICES Ltd. |

7.0 2008 EXPLORATION PROGRAM

The 2008 exploration program consisted of stream sediment sampling, soil geochemical sampling prospecting and rock sampling and construction of approximately 2.0 km of access trail. The program involved the collection of 15 stream sediment samples, 29 soil samples and 44 rock samples.

Stream sediment samples were collected by sieving the stream silts in a #12 mesh sieve and placing the -12 mesh material in an appropriately labelled Kraft wet-strength sample bag. A GPS recording was taken at each sample site. At all sample sites the creek was narrow and shallow and in some locations, on steeper sections of the creek, it was difficult to locate fine material. Stream sediment sample locations are provided in Figure 5.

Soil samples were collected using a mattocks to dig 20 to 30 cm in “B” to “C” horizon material above the upper bank of the creek. Approximately 0.5 kg of sandy-silty material was collected and placed in a labelled Kraft bag. Soil sample locations are provided in Figure 8.

Rock samples were “grab” samples of float and from outcrop. Rock samples were placed in plastic poly bags labelled with the sample number. Locations were marked in the field with flagging and a GPS coordinate was recorded at each site. Rock sample descriptions are included in Appendix II and locations are provided in Figures 11, 12 and 13.



Photo 1. Lower part of ATV access trail



Photo 2. Upper part of ATV access trail



Photo 3. Little Hyland River valley from top of Golden Culvert Property

8.0 GEOCHEMICAL ANALYTICAL PROCEDURE

Samples from the 2008 program were sent to ALS Chemex Labs in North Vancouver. The soil and stream sediment samples were handled in the same manner. The samples were sieved in a 180 um sieve then analysed for 48 elements by four acid digestion with Inductively coupled plasma mass spectroscopy (ICP-MS) according to the ME-MS61 procedure. As well, each sample was analysed for gold by fire assay with atomic absorption finish according to the Au-ICP21 procedure.

Rock samples were processed by crushing to 70% < 2 mm and pulverizing 200 grams of the < 2 mm material to 85% < 75 um according to the Prep 21 lab procedure. The pulverized material was then analysed by ME-MS61 for 48 elements and for gold by Au-ICP21 as for the soil and stream sediments. Samples that returned greater than 10000 ppm gold were also analysed by fire assay with gravimetric finish according to the Au-GRA21 procedure.

Analytical certificates are included in Appendix III and plots of sample locations, gold and arsenic results are included with samples collected from previous years in Figures 5 through 13.

9.0 INTERPRETATION AND CONCLUSIONS

The results from the 2008 exploration program on the Golden Culvert Property are very encouraging. The follow up work on the property was successful in locating sources of gold mineralization in the headwaters of the main creek draining the eastern part of the property and also located gold mineralization 1.2 km northwest of there.

Statistics from all samples collected on the property to date are as follows:

| Sample type | Element | Minimum | Maximum | Mean | Standard Dev. | Population |
|-----------------|---------------|---------|---------|---------|---------------|------------|
| Stream Sediment | Gold (ppm) | 0.001 | 1.845 | 0.169 | 0.368 | 38 |
| | Arsenic (ppm) | 2.3 | 138.5 | 48.2 | 38.1 | 38 |
| Soil | Gold (ppm) | <.005 | 0.244 | 0.024 | 0.053 | 35 |
| | Arsenic (ppm) | <2 | 203.0 | 37.8 | 43.9 | 35 |
| Rock | Gold (ppm) | <.001 | 17.300 | 1.389 | 3.293 | 44 |
| | Arsenic (ppm) | 2.3 | >10,000 | 1,558.8 | 2,981.8 | 44 |

The stream sediment sampling program focussed on streams in the north eastern and western parts of the property. This program did not return any new gold anomalies, however it did return some significant arsenic results in the northern and eastern part of the property. Two samples collected from the unnamed creek north of the main creek returned 136.5 and 124.0 ppm As. These numbers are significant and point to a source of arsenic in the northern part of the property. Arsenic is an important pathfinder element on the property and regionally. Gold mineralization generally occurs with

arsenopyrite in quartz veins as is demonstrated by the geochemistry of rock samples collected on the property to date.

The soil sampling program focused on the main showing area near the head waters of the main creek draining the eastern part of the property. A few soil samples were collected in the far north eastern part of the property and one sample was collected in the western part of the property. The samples collected in the main showing area returned some significantly anomalous coincident gold and arsenic results as can be seen on Figures 9 and 10. Gold in soil values are as high as 0.244 ppm and arsenic values as high as 203 ppm. The sampling in the far north eastern part of the property returned one moderately anomalous arsenic value of 66.4 ppm and no significant gold values. The one sample collected on the western part of the property did not return any significant results.

The prospecting and rock sampling portion of the program was successful in locating a number of sources of gold mineralization in the headwaters of the main creek. Of 14 samples collected in the immediate area, 9 returned values ranging from 1.630 to 17.30 grams/tonne gold. Arsenic concentrations in these samples ranged from 27.3 to >10,000 ppm. In general, there is good coincidence of arsenic with gold. Based on observation of the representative samples provided by Mr. Lee, it appears that gold is concentrated in quartz veins with arsenopyrite. Although, not all samples of quartz-bearing material returned anomalous gold values, not all samples containing significant concentrations of gold returned anomalous arsenic concentrations and not all samples with anomalous arsenic contained any appreciable gold. The photo below shows the terrain 1 km below the showing and Photo 5 is the main showing.



Photo 4. Looking up main creek towards the main showing (showing is 800 m upstream from the bend)



Photo 5. Main showing quartz vein at headwaters of the main creek

A second area of significant gold mineralization occurs 1.2 km to the northwest of the main creek showing. At sample station WP-17 a sample of quartz vein material with pyrite and traces of arsenopyrite returned 4.170 g/t gold and 2860 ppm arsenic. Two other samples collected in the area (C-OC7 and WP-17A) returned anomalous arsenic values of 2100 and 6910 ppm but were not anomalous in gold. It is possible that this mineralized structure may be the source of the arsenic in stream sediments in the northern creek.

One structural measurement was obtained during the 2008 program. It was measured from the quartz vein at sample location C-OC2 (graded 17.30 g/t gold). The measurement showed a strike of 120° and a steep, near vertical dip to the quartz vein. This measurement corroborates the trend of anomalous rock samples observed to the southeast and the anomalous sample located 1.2 km to the northwest.

10.0 RECOMMENDATIONS

Recommendations for future work on the property are to expand the soil sampling program with a grid covering the area of anomalous rock and soil samples and extending north and south of there. Further prospecting should be conducted throughout the property. The stream sediment sampling program has proven to be a useful tool on the property to locate areas of anomalous gold and arsenic mineralization. Additional stream sediment sampling is warranted to cover all streams on the property, especially in the north eastern corner of the claims.

The property should be geologically mapped and a structural interpretation may be helpful to locate vein sets. A ground magnetic survey is recommended to delineate the airborne magnetic high feature as it may be reflecting a buried intrusion, which could be important in the mineralizing process. A VLF-EM survey may also assist in delineating important structures on the property. Finally, the showing areas in the main creek and at sample site WP-17 should be hand or blast trenched to better expose the mineralization and trace it along strike. The budget for the proposed program is estimated at \$200,000.

Respectfully Submitted,

Scott Casselman, B.Sc., P.Geo
Geologist

11.0 STATEMENT OF EXPENDITURES

| | |
|--|---------------------|
| Labour | |
| Gary Lee* – 30 days @ \$325 | \$9,750.00 |
| Ron Stack – 26 days @ \$325 | 8,450.00 |
| Truck rental – 7 weeks @ \$500/week | 3,500.00 |
| ATV rentals – 2 ATV for 4 weeks and 1 for 3 weeks @ \$700/wk | 7,700.00 |
| ATV trailer rental – 1.75 months at \$500/month | 875.00 |
| Room and Board – 56 man-days @ \$75.00 /day | 4,200.00 |
| Chain saw rental – 14 days @ \$35.00 /day | 490.00 |
| Canoe rental | 300.00 |
| Satellite phone rental | 555.00 |
| Assaying charges | 3,885.89 |
| Expenses (supplies, freight, fuel, airphotos, etc) | 1,567.99 |
| Report Writing, map preparation, reproduction and binding– Casselma Geological Services | <u>840.00</u> |
| Total | <u>\$ 42,113.88</u> |

* Note – Gary Lee’s labour costs do not include days in which he was claim staking, thus qualifying for assessment purposes.

12.0 REFERENCES

- Casselmann, S. G., 2007. 2006/2007 Soil and Stream Sediment Sampling Program on the Culvert Property, Tungsten Area, Yukon Territory. Private Report.
- DIAND, 2002. Yukon Minfile, Exploration and Geological Services Division, Yukon, Indian and Northern Affairs Canada.
- Doherty, R. A. and vanRanden, J. A., 1994. Report on the 1993 Geological and Geochemical Assessment Work on the Tuna Property. Yukon Territorial Government assessment report # 093175.
- Gordey, S.P., Makepeace, A.J., (compilers), 2000. Yukon Digital Geology, Geological Survey of Canada, Open File D3826.
- Hart, C. J. R. and Lewis, L. L., 2005. Gold Mineralization in the Upper Hyland River Area: A Non-magmatic origin. Yukon Exploration and Geology , 2205. PP 109-125.
- Heon, D, 2007. Selwyn Basin Metallogeny. Yukon Geological Survey Website, www.geology.gov.yk.ca/metallogeny/selwyn.

APPENDIX I

STATEMENT OF QUALIFICATIONS

STATEMENT OF QUALIFICATIONS

I, Scott Casselman, of 33 Firth Road, Whitehorse, Yukon Territory, certify that

- 1) I am a geologist employed by Casselman Geological Services of Whitehorse, Yukon Territory.
- 2) I graduated from Carleton University in Ottawa, Ontario with a Bachelor of Science Degree in Geology in 1985 and have worked as a geologist since that time
- 3) I am a Professional Geoscientist registered with the Association of Professional Engineers and Geoscientists of British Columbia, Registration No. 20032.
- 4) I am responsible for preparation of this report based on information provided to me by Mr. Gary Lee and on original analytical certificates provided by the ALS Chemex laboratories Ltd.
- 5) I have not visited the Culvert Property.

Dated 20th of December, 2008.

Scott Casselman, P.Geo.

APPENDIX II
ROCK SAMPLE DESCRIPTIONS

CULVERT PROPERTY 2008 ROCK SAMPLE DESCRIPTIONS

| Sample | NAD 83 UTM E | NAD 83 UTM N | Description |
|------------|--------------|--------------|---|
| C-ARF1 | 528842 | 6867398 | Ferricrete cemented breccia. Angular clasts generally less than 1.5 cm. Some clasts altered to orange, iron-rich clay. |
| C-ARF2 | 527741 | 6867242 | Muscovite schist/phyllite with 10 to 15% medium-grained disseminated pyrite cubes. |
| C-ARF3 | 527269 | 6866130 | 3 cm wide bull white quartz vein in green, chlorite-rich schistose rock. No sulphides visible. |
| C-ARF4 | 527186 | 6866106 | Bull white quartz vien in green shistose rock (meta-volcanic?). |
| C40-ARIDGE | | | Brecciated, siliceous rock with 20% limonite-rich clay filling matrix and vugs. |
| WP-03 | 528017 | 6867188 | Dark grey siltstone with yellow-orange clayey coating (after arsenopyrite?). |
| WP-04 | 531043 | 6868480 | Grey phyllite with 2 mm wide white quartz vein. 2% fine to medium grained pyrite cubes in quartz vein. |
| WP-05 | 531239 | 6868530 | Brecciated green schistose rock (meta-volcanic?) with 25% bull-white quartz filling matrix. No sulphides. |
| WP-06 | 531302 | 6868579 | Muscovite schist - metasediment (?). 8 to 10% quartz veining with red iron staining. 5 to 7% medium grained, euhedral pyrite. |
| WP-07 | 529593 | 6870312 | Bull white quartz vein in argillite. Some iron oxide staining on fractures. No sulphides evident. |
| WP-08 | 531611 | 6868413 | Vuggy, bull white quartz filling with abundant limonite coating. No sulphides evident. |
| WP-09A | 531568 | 6868482 | Bleached meta-sandstone / siltstone with 10% quartz veining and 7 to 10% coarse, euhedral, disseminated pyrite cubes. |
| WP-09B | 531568 | 6868482 | Brecciated, green schistose rock (meta-volcanic ?) with 15% quartz filling (quartz is iron stained) and 3 to 5% coarse, euedral pyrite. |
| WP-10 | 527182 | 6866333 | Green-grey phyllite with minor iron staining on fractures. No sulphides evident. |
| WP-11A | 526736 | 6866452 | Bull white quartz lense in phyllitic schist. 5% coarse euhedral pyrite. |
| WP-11B | 526736 | 6866452 | Muscovite schist - metasediment (?). 15 to 20% very coarse grained, euhedral pyrite. |
| WP-17 | 530530 | 6869790 | Orangey-white quartz vein in phyllite. 2% medium-grained pyrite cubes and possible traces of rsenopyrite. |
| WP-17A | 530533 | 6869790 | Orangey-white quartz vein in phyllite/meta-sediments. 2% medium-grained pyrite cubes and possible traces of rsenopyrite. |
| WP-18 | 530830 | 6869963 | Bleached meta-sandstone / siltstone with 1 cm quartz veining and 15 % coarse, euhedral, disseminated pyrite cubes in qtz vein and host rock. |
| WP-19 | 531713 | 6868671 | Bleached meta-sandstone / siltstone with 0.5 cm quartz veining and 5 % fine to medium-grained, euhedral, disseminated pyrite cubes in qtz vein and host rock. |
| WP-20 | 531878 | 6868833 | Dark green phyllite with 30% white, wispy quartz veining and 5% coarse-grined pyrite. |
| WP-21 | 531435 | 6868545 | Sugary, bull white quartz breccia with moderate amount of limonite staining. No sulphides evident. |
| WP-22 | 531541 | 6868937 | Green phyllite with minor white quartz veining and 5% medium-grained euhedral pyrite. |

CULVERT PROPERTY 2008 ROCK SAMPLE DESCRIPTIONS

| Sample | NAD 83 UTM E | NAD 83 UTM N | Description |
|---------|--------------|--------------|--|
| WP-23 | 531265 | 6868813 | Brecciated green schistose rock and quartz. Traces of very fine-grained pyrite. |
| C-BODR | | | Dark grey, shaley phyllite with 3 cm wide bull white quartz vein and 2 % medium-grained, pyrite. |
| C-OC1 | 529193 | 6870096 | Grey phyllite with 1 cm wide white quartz fracture filling. Traces of very fine grained pyrite in quartz vein. |
| C-OC2 | 531128 | 6868868 | Bull white quartz vein with traces of arsenopyrite and 3% disseminated, fine-grained pyrite cubes. |
| C-OC3 | 531132 | 6868873 | |
| C-OC4 | 531072 | 6868848 | green-grey phyllite with 10% quartz veining and 2% fine-grained disseminated pyrite. |
| C-OC5 | 531087 | 6868845 | green-grey phyllite with 5% quartz veining and 1-2% fine-grained disseminated pyrite and 1 to 2% arsenopyrite in foliation planes. |
| C-OC6 | 531087 | 6868844 | green-grey phyllite with 10% quartz veining and 2% fine-grained disseminated pyrite and 1 to 2% arsenopyrite in foliation planes. |
| C-OC7 | 530681 | 6869842 | Bull white quartz vein with dark grey hematite and traces of arsenopyrite. |
| C-RF1 | 531262 | 6868706 | Bull White quartz vein with minor limonite staining and 2% disseminated pyrite. Vein cuts meta-sediment. |
| C-RF2 | 530959 | 6868904 | |
| C-RF3 | 529564 | 6870428 | Bull white quartz vein in argillite. No sulphides evident. |
| C-RF4 | 531107 | 6868880 | Rusty, white quartz vein cutting meta-sediments. 3 to 5% medium-grained pyrite cubes in quartz. |
| C-RF5 | 531523 | 6869494 | Grey, micaceous phyllite with minor quartz veining and traces of very fine-grained pyrite. |
| C-RF6 | 530695 | 6868632 | Bull white quartz vein in phyllite. No sulphides evident. |
| C-RF7 | 531057 | 6868903 | Bull white quartz vein in phyllite. No sulphides evident. |
| C-RF8T | 531061 | 6868880 | White quartz vein with pitted-out pyrite vugs filled with limonite and 5% medium-grained euhedral pyrite and traces of arsenopyrite. |
| C-RF9T | 531064 | 6868887 | Orangey-white quartz vein with 3 to 5% fine-grained wispy arsenopyrite and rusty-manganese coating on fractures. |
| C-RF10 | 531070 | 6868892 | Grey phyllite with 1 cm rusty, white quartz vein. No sulphides evident. |
| C-Mo | 526570 | 6875800 | 1 cm wide, bull white quartz vein with abundant limonite and goethite staining in a micaceous schist. |
| CVRT-49 | | | Bull white quartz vein with a sugary texture. Muscovite and weathered pyrite to 10%. |

APPENDIX III
GEOCHEMICAL ANALYTICAL CERTIFICATES



ALS Chemex
EXCELLENCE IN ANALYTICAL CHEMISTRY

ALS Canada Ltd.

212 Brooksbank Avenue
 North Vancouver BC V7J 2C1

Phone: 604-984-0221 Fax: 604-984-0218 www.alschemex.com

To: LEE, GARY
 P.O. BOX 31800
 WHITEHORSE YT Y1A 6L3

Page: 1
 Finalized Date: 25-JUL-2008
 This copy reported on 28-JUL-2008
 Account: LEEGAR

CERTIFICATE VA08094694

Project:
 P.O. No.:
 This report is for 37 Rock samples submitted to our lab in Vancouver, BC, Canada on 7-JUL-2008.
 The following have access to data associated with this certificate:
 GARY LEE
 BOB SCOTT

| SAMPLE PREPARATION | |
|--------------------|--------------------------------|
| ALS CODE | DESCRIPTION |
| WEI-21 | Received Sample Weight |
| LOG-22 | Sample login - Rcd w/o BarCode |
| CRU-31 | Fine crushing - 70% <2mm |
| SPL-21 | Split sample - riffle splitter |
| PUL-31 | Pulverize split to 85% <75 um |

| ANALYTICAL PROCEDURES | |
|-----------------------|-----------------------------|
| ALS CODE | DESCRIPTION |
| ME-MS61 | 48 element four acid ICP-MS |
| Au-ICP21 | Au 30g FA ICP-AES Finish |
| Au-GRA21 | Au 30g FA-GRAV finish |
| | ICP-AES |
| | WST-SIM |

To: LEE, GARY
 P.O. BOX 31800
 WHITEHORSE YT Y1A 6L3

This is the Final Report and supersedes any preliminary report with this certificate number. Results apply to samples as submitted. All pages of this report have been checked and approved for release.

Signature:

Colin Ramshaw, Vancouver Laboratory Manager



ALS Chemex
EXCELLENCE IN ANALYTICAL CHEMISTRY

ALS Canada Ltd.
212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: LEE, GARY
P.O. BOX 31800
WHITEHORSE YT Y1A 6L3

Page: 2 - A
Total # Pages: 2 (A - D)
Plus Appendix Pages
Finalized Date: 25-JUL-2008
Account: LEEGAR

CERTIFICATE OF ANALYSIS VA08094694

| Method Analyte Units LOR | WEI-21 Recvd Wt. kg | Au-ICP21 Au ppm | Au-GRA21 Au ppm | ME-MS61 Ag ppm | ME-MS61 Al % | ME-MS61 As ppm | ME-MS61 Ba ppm | ME-MS61 Be ppm | ME-MS61 Bi ppm | ME-MS61 Ca % | ME-MS61 Cd ppm | ME-MS61 Ce ppm | ME-MS61 Co ppm | ME-MS61 Cr ppm | ME-MS61 Cs ppm |
|--------------------------|---------------------|-----------------|-----------------|----------------|--------------|----------------|----------------|----------------|----------------|--------------|----------------|----------------|----------------|----------------|----------------|
| C40-ARIDGE | 0.20 | 0.032 | | 0.32 | 2.55 | 4 | 420 | 2.74 | 0.18 | 0.08 | 0.37 | 31 | 1.7 | 37 | 13 |
| C-BODR | 0.68 | 0.004 | | 0.29 | 6.3 | 2.4 | 390 | 2.31 | 0.42 | 0.05 | 0.08 | 87.5 | 8.8 | 72 | 4.23 |
| C-MO | 0.50 | 0.006 | | 0.05 | 3.82 | 39 | 80 | 0.75 | 0.68 | 0.13 | 0.02 | 41 | 7.3 | 29 | 3.06 |
| C-ARF1 | 0.50 | 0.002 | | 0.05 | 4.52 | 11.1 | 400 | 1.44 | 0.26 | 0.04 | 0.08 | 67.3 | 3.3 | 43 | 4.18 |
| C-ARF2 | 0.52 | 0.003 | | 1.52 | 8.11 | 12.4 | 210 | 2.46 | 23.5 | 0.07 | 0.04 | 91.9 | 188 | 63 | 11.4 |
| C-ARF3 | 0.70 | 0.002 | | 0.04 | 2.79 | 7.1 | 220 | 0.62 | 0.81 | 0.09 | <0.02 | 27.6 | 10.6 | 40 | 1.6 |
| C-ARF4 | 0.88 | 0.001 | | 0.15 | 3.46 | 2.3 | 70 | 0.57 | 0.38 | 0.05 | 0.02 | 27.2 | 16.4 | 35 | 0.86 |
| C-RF1 | 0.92 | 1.780 | | 0.2 | 2.32 | 2720 | 120 | 1 | 1.71 | 0.01 | 0.1 | 23.3 | 2.5 | 37 | 2.85 |
| C-RF2 | 0.46 | 0.007 | | 0.02 | 0.25 | 20.1 | 10 | 0.14 | 1.04 | 0.02 | 0.07 | 4.39 | 0.9 | 25 | 0.3 |
| C-RF3 | 0.80 | 0.008 | | 0.2 | 5.67 | 3.6 | 210 | 1.6 | 0.84 | 0.14 | 0.05 | 68.5 | 26 | 53 | 2.59 |
| C-RF4 | 0.84 | 9.48 | | 0.45 | 2.07 | >10000 | 120 | 0.84 | 2.3 | 0.04 | 0.08 | 18.25 | 2.5 | 34 | 2.62 |
| C-RF5 | 1.52 | 0.013 | | <0.01 | 4.16 | 20 | 130 | 1.02 | 0.16 | 0.07 | <0.02 | 36 | 6.9 | 64 | 2.17 |
| C-OC1 | 0.42 | 0.003 | | 0.08 | 6.65 | 9.9 | 260 | 2.05 | 0.67 | 0.07 | <0.02 | 67.6 | 4.5 | 57 | 3.85 |
| C-OC2 | 0.76 | >10.0 | 17.30 | 0.28 | 0.43 | 6620 | 20 | 0.1 | 11.85 | 0.01 | 0.03 | 3.41 | 0.5 | 21 | 0.31 |
| C-OC3 | 1.02 | 8.28 | | 0.1 | 3.32 | 9010 | 180 | 1.19 | 0.55 | 0.02 | <0.02 | 25.2 | 2 | 32 | 2.39 |
| C-OC4 | 1.20 | 1.630 | | 0.06 | 10.45 | 93.2 | 690 | 4.42 | 0.96 | 0.06 | <0.02 | 141.5 | 15.2 | 86 | 13.05 |
| C-OC5 | 1.62 | 2.47 | | 0.09 | 10.35 | 9630 | 630 | 4.3 | 1.13 | 0.05 | 0.02 | 123.5 | 24.6 | 83 | 11.3 |
| C-OC6 | 1.58 | 3.28 | | 0.06 | 9.82 | 6350 | 580 | 4.07 | 1.38 | 0.06 | <0.02 | 124.5 | 21.9 | 86 | 9.9 |
| C-OC7 | 1.50 | 0.080 | | 5.32 | 0.87 | 2100 | 40 | 0.29 | 37.9 | 0.02 | 1 | 10.85 | 1.8 | 31 | 1.12 |
| WP-03 | 0.26 | 0.007 | | 0.07 | 10.45 | 44.1 | 2010 | 3.64 | 0.55 | 0.06 | <0.02 | 131.5 | 36.8 | 78 | 21.8 |
| WP-04 | 0.54 | 0.300 | | 0.28 | 4.86 | 55.9 | 80 | 0.8 | 4.7 | 0.09 | 0.04 | 51.9 | 25.2 | 37 | 2.39 |
| WP-05 | 0.82 | 0.002 | | 0.13 | 3.99 | 15.8 | 160 | 0.53 | 0.49 | 0.09 | 0.04 | 16.35 | 18.9 | 21 | 2.07 |
| WP-06 | 0.90 | 0.003 | | 0.52 | 9.84 | 32 | 360 | 3.53 | 1.61 | 0.08 | <0.02 | 105 | 24.1 | 75 | 8.72 |
| WP-07 | 0.46 | 0.003 | | 0.2 | 4.23 | 37.6 | 180 | 1.3 | 0.83 | 0.16 | <0.02 | 49.6 | 15.5 | 34 | 1.91 |
| WP-08 | 0.58 | 0.002 | | 0.1 | 3.22 | 7.3 | 10 | 0.45 | 0.14 | 0.6 | 0.08 | 38.9 | 20.2 | 21 | 1.12 |
| WP-09A | 0.52 | 0.020 | | 0.45 | 4.16 | 66 | 10 | 0.68 | 14.2 | 0.12 | 28.2 | 32.5 | 9.2 | 23 | 0.65 |
| WP-09B | 1.68 | 0.047 | | 0.51 | 4.27 | 527 | 20 | 0.68 | 8.48 | 0.06 | 0.13 | 27 | 7 | 17 | 1.58 |
| WP-10 | 0.92 | 0.002 | | 0.06 | 9.22 | 23.7 | 510 | 3.12 | 0.39 | 0.07 | <0.02 | 138.5 | 5.6 | 87 | 5.38 |
| WP-11A | 1.40 | 0.002 | | 0.6 | 5.26 | 18.2 | 90 | 1.02 | 4.23 | 0.61 | 0.24 | 58.2 | 41.2 | 39 | 1.05 |
| WP-11B | 0.88 | 0.003 | | 0.06 | 5.14 | 14.3 | 90 | 1.82 | 6.06 | 0.04 | <0.02 | 43.7 | 46.1 | 29 | 2.88 |
| WP-17 | 1.28 | 4.17 | | 0.24 | 3.13 | 2860 | 130 | 0.88 | 0.5 | 0.03 | 0.11 | 38 | 5 | 31 | 2.52 |
| WP-18 | 0.82 | 0.010 | | 2.58 | 3.63 | 31.4 | 50 | 0.59 | 36.2 | 0.13 | 0.14 | 37.6 | 10.7 | 29 | 1.42 |
| WP-19 | 0.56 | 0.015 | | 2.97 | 3.39 | 21.2 | 40 | 1.46 | 87.2 | 0.33 | 59.8 | 37.4 | 12.7 | 36 | 1.9 |
| WP-20 | 0.82 | 0.002 | | 0.04 | 8.88 | 22.5 | 460 | 2.08 | 1.09 | 0.06 | 0.2 | 87.1 | 9.9 | 68 | 6.42 |
| WP-21 | 0.96 | 0.211 | | 0.26 | 1.41 | 116 | 10 | 0.42 | 11.9 | 0.03 | 0.62 | 15.5 | 2.2 | 23 | 0.3 |
| WP-23A | 0.98 | 0.019 | | 0.17 | 1.34 | 21.1 | 20 | 0.88 | 0.91 | 0.04 | <0.02 | 24.6 | 8.9 | 27 | 1.04 |
| WP-23B | 1.18 | 3.12 | | 0.25 | 4.93 | 27.3 | 120 | 1.82 | 0.76 | 0.47 | 0.06 | 51.8 | 12.6 | 44 | 2.82 |



ALS Chemex
 EXCELLENCE IN ANALYTICAL CHEMISTRY

ALS Canada Ltd.
 212 Brooksbank Avenue
 North Vancouver BC V7J 2C1
 Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: LEE, GARY
 P.O. BOX 31800
 WHITEHORSE YT Y1A 6L3

Page: 2 - C
 Total # Pages: 2 (A - D)
 Plus Appendix Pages
 Finalized Date: 25-JUL-2008
 Account: LEEGAR

CERTIFICATE OF ANALYSIS VA08094694

| Method Analyte Units LOR | ME-MS61 P ppm | ME-MS61 Pb ppm | ME-MS61 Rb ppm | ME-MS61 Re ppm | ME-MS61 S % | ME-MS61 Sb ppm | ME-MS61 Sc ppm | ME-MS61 Se ppm | ME-MS61 Sn ppm | ME-MS61 Sr ppm | ME-MS61 Ta ppm | ME-MS61 Te ppm | ME-MS61 Th ppm | ME-MS61 Ti % | ME-MS61 Tl ppm |
|--------------------------|---------------|----------------|----------------|----------------|-------------|----------------|----------------|----------------|----------------|----------------|----------------|----------------|----------------|--------------|----------------|
| C40-ARIDGE | 120 | 14.4 | 47.7 | <0.002 | 0.04 | 5.99 | 3.7 | 1 | 2 | 51.3 | 0.29 | <0.05 | 5 | 0.108 | 0.54 |
| C-BODR | 720 | 30.8 | 92.8 | <0.002 | 0.09 | 1.92 | 11.3 | 1 | 2.5 | 84.1 | 0.9 | 0.17 | 13.9 | 0.316 | 0.46 |
| C-MO | 380 | 24.8 | 32.5 | <0.002 | 0.68 | 0.47 | 5.3 | 1 | 0.8 | 37.7 | 0.3 | <0.05 | 7.7 | 0.102 | 0.16 |
| C-ARF1 | 500 | 10 | 81.2 | <0.002 | 0.1 | 0.32 | 8 | 1 | 1.4 | 57.8 | 0.32 | <0.05 | 8.9 | 0.124 | 0.42 |
| C-ARF2 | 580 | 162.5 | 107.5 | <0.002 | 4.22 | 0.45 | 11.3 | 3 | 2.2 | 84.7 | 0.67 | 1 | 13.8 | 0.26 | 0.59 |
| C-ARF3 | 290 | 6.4 | 30.1 | <0.002 | 0.03 | 0.11 | 3.9 | 1 | 0.7 | 33.3 | 0.15 | <0.05 | 4 | 0.055 | 0.13 |
| C-ARF4 | 230 | 18.1 | 19.1 | <0.002 | 0.02 | 1.06 | 4.5 | 1 | 0.5 | 16.2 | 0.14 | <0.05 | 4 | 0.059 | 0.09 |
| C-RF1 | 40 | 16.2 | 49.5 | <0.002 | 0.29 | 1.67 | 3.1 | 1 | 4 | 28.9 | 0.21 | 0.06 | 5.1 | 0.077 | 0.26 |
| C-RF2 | 40 | 3.1 | 2.3 | <0.002 | 0.01 | 0.17 | 0.6 | 1 | 0.6 | 4 | <0.05 | <0.05 | 1.4 | 0.011 | <0.02 |
| C-RF3 | 230 | 39 | 62.7 | <0.002 | 0.03 | 1.18 | 9.2 | 1 | 1.8 | 52.6 | 0.47 | 0.08 | 9.8 | 0.178 | 0.3 |
| C-RF4 | 200 | 9.5 | 48.6 | <0.002 | 0.66 | 7.17 | 2.9 | 1 | 3.6 | 22.3 | 0.17 | 0.09 | 3.7 | 0.069 | 0.23 |
| C-RF5 | 220 | 10.8 | 36.5 | <0.002 | 0.01 | 0.22 | 4.9 | 1 | 1.3 | 47.1 | 0.32 | <0.05 | 6.7 | 0.164 | 0.17 |
| C-OC1 | 430 | 48 | 104.5 | <0.002 | 0.04 | 0.8 | 12.9 | 1 | 2 | 51 | 0.53 | <0.05 | 12.2 | 0.192 | 0.51 |
| C-OC2 | 20 | 22.6 | 4.8 | <0.002 | 0.16 | 2.49 | 0.5 | 1 | 0.6 | 9.1 | <0.05 | 0.14 | 0.6 | 0.019 | 0.02 |
| C-OC3 | 50 | 8.7 | 51.3 | <0.002 | 0.6 | 3.46 | 3.8 | 1 | 0.8 | 24.7 | 0.19 | <0.05 | 4.2 | 0.1 | 0.25 |
| C-OC4 | 450 | 17.9 | 218 | <0.002 | 1.01 | 1.63 | 22.3 | 2 | 3.7 | 135 | 0.81 | 0.06 | 23.4 | 0.225 | 1.16 |
| C-OC5 | 270 | 20.6 | 206 | <0.002 | 0.97 | 2.78 | 20.1 | 2 | 7.4 | 123.5 | 0.72 | 0.12 | 21.8 | 0.234 | 1.09 |
| C-OC6 | 340 | 17.1 | 195 | <0.002 | 0.76 | 1.92 | 20.8 | 2 | 10.1 | 121.5 | 0.77 | 0.11 | 21.8 | 0.216 | 1.06 |
| C-OC7 | 70 | 398 | 11 | <0.002 | 0.06 | 2.83 | 1.6 | 2 | 1.4 | 19.2 | 0.07 | 0.15 | 1.5 | 0.028 | 0.07 |
| WP-03 | 420 | 21.7 | 132.5 | <0.002 | 0.95 | 3.27 | 17.9 | 1 | 2.6 | 142.5 | 0.56 | <0.05 | 20.9 | 0.119 | 1.44 |
| WP-04 | 560 | 22.4 | 30.7 | <0.002 | 0.63 | 0.35 | 5.5 | 2 | 2.5 | 28.1 | 0.28 | 0.07 | 12.4 | 0.082 | 0.16 |
| WP-05 | 290 | 11.2 | 21.4 | <0.002 | 0.08 | 0.71 | 4.3 | 1 | 2.3 | 42.4 | 0.13 | <0.05 | 2.7 | 0.049 | 0.11 |
| WP-06 | 470 | 496 | 111 | <0.002 | 1.08 | 0.63 | 17.4 | 2 | 5.4 | 164 | 0.87 | 0.06 | 19 | 0.287 | 0.59 |
| WP-07 | 720 | 20.1 | 44.5 | <0.002 | 0.06 | 0.26 | 7.1 | 2 | 1.6 | 52.3 | 0.3 | <0.05 | 6.9 | 0.114 | 0.22 |
| WP-08 | 420 | 14 | 4.4 | <0.002 | 0.38 | 0.72 | 3.3 | 2 | 0.8 | 89.6 | 0.22 | <0.05 | 8 | 0.066 | 0.04 |
| WP-09A | 420 | 30.2 | 2.7 | <0.002 | 0.96 | 0.38 | 4 | 2 | 7.8 | 65.1 | 0.19 | 0.1 | 9.8 | 0.069 | 0.05 |
| WP-09B | 490 | 20.4 | 3.8 | <0.002 | 0.31 | 0.43 | 5.1 | 2 | 3.4 | 65.7 | 0.1 | 0.08 | 4.7 | 0.037 | 0.02 |
| WP-10 | 660 | 31.7 | 168 | <0.002 | 0.33 | 1.4 | 17.8 | 2 | 3.1 | 71.5 | 1.13 | <0.05 | 21.6 | 0.079 | 0.79 |
| WP-11A | 860 | 165.5 | 29.3 | <0.002 | 1.17 | 0.21 | 6.1 | 3 | 0.9 | 68.9 | 0.21 | 0.11 | 10.6 | 0.061 | 0.14 |
| WP-11B | 220 | 10.1 | 84.4 | <0.002 | 8.15 | 0.26 | 7.5 | 4 | 1.7 | 82.5 | 0.45 | 0.87 | 12.5 | 0.139 | 0.4 |
| WP-17 | 210 | 8.9 | 38.7 | <0.002 | 0.12 | 1.91 | 4.2 | 2 | 2.4 | 39.8 | 0.32 | <0.05 | 9.3 | 0.112 | 0.19 |
| WP-18 | 540 | 29.1 | 18 | 0.003 | 0.11 | 0.66 | 4.1 | 2 | 5.7 | 37.5 | 0.23 | 0.18 | 11 | 0.08 | 0.09 |
| WP-19 | 340 | 182.5 | 13.2 | <0.002 | 1.62 | 1.46 | 4.7 | 3 | 6.4 | 103.5 | 0.27 | 0.48 | 11.9 | 0.091 | 0.08 |
| WP-20 | 320 | 19.8 | 141.5 | <0.002 | 0.24 | 0.27 | 11.3 | 2 | 2.9 | 76.7 | 0.59 | <0.05 | 18.5 | 0.178 | 0.72 |
| WP-21 | 170 | 14.4 | 1 | <0.002 | 0.02 | 0.58 | 1.5 | 2 | 3.1 | 24.2 | 0.07 | 0.07 | 3.7 | 0.03 | <0.02 |
| WP-23A | 100 | 16.3 | 9.1 | <0.002 | 0.27 | 1.18 | 10.3 | 3 | 2.3 | 35.3 | 0.11 | 0.06 | 3.9 | 0.046 | 0.06 |
| WP-23B | 100 | 30 | 54.6 | <0.002 | 1.52 | 0.53 | 8.1 | 2 | 1.4 | 102 | 0.46 | <0.05 | 9.3 | 0.17 | 0.25 |



ALS Chemex
EXCELLENCE IN ANALYTICAL CHEMISTRY

ALS Canada Ltd.
 212 Brooksbank Avenue
 North Vancouver BC V7J 2C1
 Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: LEE, GARY
 P.O. BOX 31800
 WHITEHORSE YT Y1A 6L3

Page: 2 - D
 Total # Pages: 2 (A - D)
 Plus Appendix Pages
 Finalized Date: 25-JUL-2008
 Account: LEEGAR

CERTIFICATE OF ANALYSIS VA08094694

| Sample Description | Method Analyte Units LOR | ME-MS61 | | ME-MS61 | | ME-MS61 | | ME-MS61 | | ME-MS61 | | | |
|--------------------|--------------------------|---------|-------|---------|-------|---------|--------|---------|-------|---------|-------|--------|--------|
| | | U ppm | V ppm | W ppm | Y ppm | Zn ppm | Zr ppm | U ppm | V ppm | W ppm | Y ppm | Zn ppm | Zr ppm |
| C40-ARIDGE | | 0.5 | 23 | 4 | 2 | 61 | 18.1 | | | | | | |
| C-BODR | | 2.7 | 98 | 1.8 | 10.2 | 80 | 73.4 | | | | | | |
| C-MO | | 1 | 28 | 0.9 | 5.4 | 72 | 33.9 | | | | | | |
| C-ARF1 | | 1.1 | 54 | 0.8 | 6.2 | 67 | 41.8 | | | | | | |
| C-ARF2 | | 1.8 | 63 | 1.6 | 7.3 | 121 | 29.2 | | | | | | |
| C-ARF3 | | 0.5 | 23 | 0.6 | 2.6 | 54 | 12.9 | | | | | | |
| C-ARF4 | | 0.7 | 29 | 0.5 | 4.5 | 95 | 12.6 | | | | | | |
| C-RF1 | | 0.7 | 22 | 3.1 | 1.9 | 29 | 13 | | | | | | |
| C-RF2 | | 0.4 | 3 | 0.6 | 0.5 | 68 | 1.6 | | | | | | |
| C-RF3 | | 1.2 | 50 | 0.9 | 8.2 | 129 | 35.6 | | | | | | |
| C-RF4 | | 0.9 | 19 | 3.2 | 2.7 | 23 | 16.2 | | | | | | |
| C-RF5 | | 1 | 35 | 0.3 | 4.2 | 61 | 27.5 | | | | | | |
| C-OC1 | | 2 | 57 | 0.6 | 12.8 | 59 | 68.8 | | | | | | |
| C-OC2 | | 0.2 | 4 | 0.6 | 0.4 | 6 | 3.6 | | | | | | |
| C-OC3 | | 0.8 | 29 | 2.3 | 3.5 | 20 | 19.1 | | | | | | |
| C-OC4 | | 3.6 | 117 | 9.8 | 13.3 | 98 | 100.5 | | | | | | |
| C-OC5 | | 3 | 97 | 8.3 | 11.5 | 72 | 80.9 | | | | | | |
| C-OC6 | | 3.1 | 87 | 7.3 | 11.4 | 81 | 83.2 | | | | | | |
| C-OC7 | | 1.9 | 8 | 0.7 | 1.3 | 70 | 5.7 | | | | | | |
| WP-03 | | 2 | 79 | 1.3 | 7.9 | 203 | 41.8 | | | | | | |
| WP-04 | | 1.6 | 35 | 5 | 6.2 | 183 | 34.3 | | | | | | |
| WP-05 | | 0.6 | 42 | 0.3 | 5.6 | 145 | 13.4 | | | | | | |
| WP-06 | | 2.4 | 89 | 1.2 | 10.9 | 99 | 87.2 | | | | | | |
| WP-07 | | 2.1 | 33 | 0.7 | 5.6 | 90 | 24.2 | | | | | | |
| WP-08 | | 1.7 | 15 | 0.6 | 6.5 | 108 | 36.1 | | | | | | |
| WP-09A | | 1.6 | 17 | 182 | 6 | 2080 | 27.3 | | | | | | |
| WP-09B | | 0.8 | 22 | 3.2 | 3.8 | 111 | 24.6 | | | | | | |
| WP-10 | | 2.8 | 86 | 1.1 | 12.4 | 60 | 118 | | | | | | |
| WP-11A | | 6.7 | 38 | 1.2 | 8.4 | 184 | 70.9 | | | | | | |
| WP-11B | | 1.3 | 37 | 1.7 | 11.3 | 38 | 48 | | | | | | |
| WP-17 | | 1.5 | 22 | 3.3 | 5 | 31 | 34.2 | | | | | | |
| WP-18 | | 2.6 | 19 | 0.8 | 7.3 | 123 | 39.3 | | | | | | |
| WP-19 | | 3.4 | 17 | 1.7 | 8.1 | 3090 | 41.5 | | | | | | |
| WP-20 | | 2.4 | 63 | 0.7 | 11.3 | 78 | 89.9 | | | | | | |
| WP-21 | | 0.9 | 4 | 2.5 | 2.1 | 112 | 16.6 | | | | | | |
| WP-23A | | 0.8 | 15 | 35.5 | 7.2 | 18 | 15 | | | | | | |
| WP-23B | | 1.4 | 38 | 5.7 | 6 | 45 | 41.5 | | | | | | |



ALS Chemex
EXCELLENCE IN ANALYTICAL CHEMISTRY

ALS Canada Ltd.

212 Brooksbank Avenue

North Vancouver BC V7J 2C1

Phone: 604 984 0221 Fax: 604 984 0218

www.alschemex.com

To: LEE, GARY

P.O. BOX 31800

WHITEHORSE YT Y1A 6L3

Page: Appendix 1

Total # Appendix Pages: 1

Finalized Date: 25-JUL-2008

Account: LEEGAR

CERTIFICATE OF ANALYSIS VA08094694

CERTIFICATE COMMENTS

Method

ME-MS61

REE's may not be totally soluble in this method.



ALS Chemex
EXCELLENCE IN ANALYTICAL CHEMISTRY
 ALS Canada Ltd.
 212 Brooksbank Avenue
 North Vancouver BC V7J 2C1
 Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: LEE, GARY
 P.O. BOX 31800
 WHITEHORSE YT Y1A 6L3

Page: 1
 Finalized Date: 1-AUG-2008
 This copy reported on 5-AUG-2008
 Account: LEEGAR


CERTIFICATE VA08094695

Project:
 P.O. No.:
 This report is for 35 Soil samples submitted to our lab in Vancouver, BC, Canada on
 7-JUL-2008.
 The following have access to data associated with this certificate:
 GARY LEE
 BOB SCOTT

| SAMPLE PREPARATION | |
|-----------------------|--------------------------------|
| ALS CODE | DESCRIPTION |
| WEI-21 | Received Sample Weight |
| LOG-22 | Sample login - Rcd w/o BarCode |
| SCR-41 | Screen to -180um and save both |
| ANALYTICAL PROCEDURES | |
| ALS CODE | DESCRIPTION |
| Au-ICP21 | Au 30g FA ICP-AES Finish |
| ME-MS61 | 48 element four acid ICP-MS |
| | INSTRUMENT |
| | ICP-AES |

To: LEE, GARY
 P.O. BOX 31800
 WHITEHORSE YT Y1A 6L3

This is the Final Report and supersedes any preliminary report with this certificate number. Results apply to samples as submitted. All pages of this report have been checked and approved for release.

Signature: 
 Colin Ramshaw, Vancouver Laboratory Manager



CERTIFICATE OF ANALYSIS VA08094695

| Method Analyte Units LOR | Sample Description | WEI-21 Recvd Wt. Kg | Au-ICP21 Au ppm | ME-MS61 Ag ppm | ME-MS61 Al % | ME-MS61 As ppm | ME-MS61 Ba ppm | ME-MS61 Be ppm | ME-MS61 Bi ppm | ME-MS61 Ca % | ME-MS61 Cd ppm | ME-MS61 Ce ppm | ME-MS61 Co ppm | ME-MS61 Cr ppm | ME-MS61 Cs ppm | ME-MS61 Cu ppm |
|--------------------------|--------------------|---------------------|-----------------|----------------|--------------|----------------|----------------|----------------|----------------|--------------|----------------|----------------|----------------|----------------|----------------|----------------|
| CS-5500E | | 0.30 | 0.004 | 0.06 | 7.22 | 25.1 | 630 | 2.11 | 1.8 | 0.48 | 0.38 | 90.4 | 14.3 | 51 | 12.6 | 27.4 |
| CS-6520E | | 0.16 | 0.001 | 0.1 | 6.62 | 2.5 | 760 | 1.28 | 0.15 | 1.6 | 0.11 | 35.5 | 7.4 | 7 | 3.62 | 17.4 |
| CS-7540E | | 0.22 | 0.009 | 0.05 | 7.18 | 17.3 | 650 | 1.89 | 0.47 | 0.93 | 0.15 | 75.4 | 12.4 | 34 | 6.03 | 23.3 |
| CS-8560E | | 0.22 | 0.004 | 0.1 | 7.79 | 37.3 | 590 | 2.76 | 0.71 | 0.44 | 0.22 | 97.6 | 17.6 | 57 | 28 | 27.2 |
| CS-9580E | | 0.20 | 0.002 | 0.05 | 6.53 | 2.3 | 780 | 1.21 | 0.14 | 1.66 | 0.04 | 32.5 | 5.1 | 7 | 1.98 | 15.9 |
| CS-10600E | | 0.14 | 0.001 | 0.06 | 6.61 | 1.9 | 810 | 1.22 | 0.11 | 1.72 | 0.04 | 30.7 | 5.3 | 5 | 1.35 | 17.1 |
| CS-11620E | | 0.28 | 0.021 | 0.11 | 7.71 | 30 | 600 | 2.12 | 0.61 | 0.56 | 0.1 | 116 | 15.4 | 51 | 6.52 | 27.9 |
| CS-12640E | | 0.18 | 0.003 | 0.07 | 6.53 | 1.8 | 800 | 1.24 | 0.12 | 1.6 | 0.05 | 31.4 | 4.3 | 4 | 1.39 | 16 |
| CS-13650E | | 0.24 | 0.067 | 0.1 | 8.57 | 119.5 | 540 | 2.71 | 0.81 | 0.23 | 0.13 | 149 | 25.5 | 69 | 8.46 | 37.3 |
| CS-14660E | | 0.22 | 0.024 | 0.09 | 7.02 | 67.8 | 640 | 1.63 | 0.48 | 0.89 | 0.07 | 85.1 | 8.4 | 34 | 4.43 | 24.3 |
| CS-15680E | | 0.22 | 0.006 | 0.1 | 6.45 | 22.5 | 760 | 1.13 | 0.15 | 1.54 | 0.07 | 32.5 | 4.6 | 6 | 1.6 | 16.3 |
| CS-16700E | | 0.28 | 0.019 | 0.09 | 8.12 | 37.3 | 510 | 2.27 | 0.86 | 0.14 | 0.12 | 149 | 20.9 | 72 | 10.15 | 29.4 |
| CS-17720E | | 0.22 | 0.008 | 0.13 | 7 | 12.6 | 750 | 1.65 | 0.28 | 1.5 | 0.26 | 49.8 | 6.3 | 15 | 3.55 | 22 |
| CS-18740E | | 0.12 | 0.003 | 0.14 | 6.73 | 2.5 | 730 | 1.22 | 0.18 | 1.66 | 0.06 | 36.3 | 5.4 | 15 | 2.08 | 19.1 |
| CS-19760E | | 0.26 | 0.013 | 0.08 | 7.35 | 20.8 | 600 | 2.45 | 0.53 | 0.73 | 0.08 | 90.4 | 16.4 | 47 | 5.95 | 37.6 |
| C-S1 | | 0.24 | 0.003 | 0.43 | 9.29 | 26 | 650 | 3.5 | 5.45 | 0.48 | 0.09 | 105 | 11.7 | 64 | 16.1 | 147.5 |
| C-S2 | | 0.38 | 0.006 | 0.23 | 9.63 | 66.4 | 740 | 3.47 | 1.3 | 0.42 | 0.08 | 126 | 41.1 | 71 | 16.7 | 67.4 |
| C-S3 | | 0.22 | 0.003 | 0.24 | 10 | 28.9 | 610 | 3.98 | 0.97 | 0.12 | 0.11 | 173.5 | 32.5 | 80 | 17.05 | 56.3 |
| C-S4 | | 0.34 | 0.002 | 0.53 | 8.98 | 33 | 630 | 2.94 | 1.12 | 0.06 | 0.15 | 138 | 20.5 | 75 | 12.6 | 42.3 |
| C-A1S | | 0.36 | 0.001 | 0.21 | 2.21 | 4.3 | 180 | 0.5 | 0.16 | 0.02 | 0.03 | 55.3 | 34.1 | 14 | 4.04 | 32.2 |
| CR-A1 | | 0.34 | 0.001 | 0.07 | 10.25 | 2.3 | 860 | 2.81 | 1.16 | 0.14 | 0.03 | 272 | 27.3 | 85 | 6.91 | 26 |
| CR-A2 | | 0.42 | 0.003 | 0.08 | 10.05 | 2.5 | 940 | 3.63 | 0.43 | 0.11 | 0.04 | 202 | 28.9 | 83 | 9 | 35.7 |
| CR-A3 | | 0.60 | 0.008 | 0.01 | 9.56 | 2.4 | 800 | 3.76 | 0.39 | 0.12 | 0.02 | 256 | 27.1 | 87 | 6.89 | 33.1 |
| CR-A4 | | 0.58 | 0.005 | 0.01 | 10.2 | 2.3 | 810 | 3.51 | 0.37 | 0.15 | 0.04 | 275 | 26.6 | 91 | 7.59 | 31.8 |
| CR-A5 | | 0.72 | 0.008 | 0.02 | 9.73 | 2.5 | 780 | 3.66 | 0.39 | 0.15 | <0.02 | 311 | 29 | 89 | 7.03 | 36.4 |
| CR-A6 | | 0.62 | 0.002 | 0.03 | 9.84 | 3 | 810 | 4.08 | 0.42 | 0.18 | 0.02 | 241 | 27.8 | 88 | 8.16 | 36.9 |
| CR-A7 | | 0.56 | 0.001 | 0.03 | 9.94 | 4.1 | 910 | 4.4 | 0.38 | 0.18 | 0.07 | 218 | 26.9 | 82 | 7.99 | 42.6 |
| CR-27 | | 0.26 | 0.005 | 0.4 | 5.15 | 29.5 | 390 | 2.79 | 0.2 | 0.95 | 0.38 | 49.9 | 12.1 | 36 | 13.7 | 69.2 |
| CR-28 | | 0.40 | 0.009 | 0.34 | 7.92 | 50.1 | 590 | 4.18 | 0.77 | 0.69 | 0.32 | 111 | 17.9 | 60 | 28 | 60.8 |
| CR-29 | | 0.38 | 0.015 | 1.05 | 8.31 | 124 | 460 | 4.88 | 0.99 | 0.38 | 0.22 | 144.5 | 36.7 | 68 | 34.5 | 89.5 |
| CR-30 | | 0.20 | 0.008 | 0.99 | 7.65 | 138.5 | 470 | 4.67 | 1.02 | 0.66 | 0.29 | 130 | 48.3 | 57 | 39.6 | 96.5 |
| CR-31 | | 0.28 | 0.018 | 0.07 | 8.65 | 62.7 | 440 | 3.62 | 0.5 | 0.16 | 0.08 | 165.5 | 32.1 | 75 | 6.91 | 122.5 |
| CR-32 | | 0.08 | 0.010 | 0.2 | 9.17 | 53.2 | 460 | 4.42 | 0.55 | 0.47 | 0.1 | 109 | 13.8 | 77 | 12.65 | 49.5 |
| CR-33 | | 0.18 | 0.003 | 0.53 | 5.7 | 41.7 | 350 | 4.59 | 0.46 | 1.2 | 0.42 | 53.3 | 12.7 | 45 | 19.05 | 108 |
| CR-34 | | 0.28 | 0.006 | 0.04 | 8.35 | 55 | 530 | 4.05 | 0.44 | 0.28 | 0.12 | 120.5 | 48.6 | 84 | 10.75 | 46.1 |



ALS Chemex
EXCELLENCE IN ANALYTICAL CHEMISTRY
 ALS Canada Ltd.

212 Brooksbank Avenue
 North Vancouver BC V7J 2C1
 Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: LEE, GARY
 P.O. BOX 31800
 WHITEHORSE YT Y1A 6L3

Page: 2 - B
 Total # Pages: 2 (A - D)
 Plus Appendix Pages
 Finalized Date: 1-AUG-2008
 Account: LEEGAR

CERTIFICATE OF ANALYSIS VA08094695

| Method Analyte Units LOR | ME-MS61 Fe % | ME-MS61 Ga ppm | ME-MS61 Ge ppm | ME-MS61 Hf ppm | ME-MS61 In ppm | ME-MS61 K % | ME-MS61 La ppm | ME-MS61 Li ppm | ME-MS61 Mg % | ME-MS61 Mn ppm | ME-MS61 Mo ppm | ME-MS61 Na % | ME-MS61 Nb ppm | ME-MS61 Ni ppm | ME-MS61 P ppm |
|--------------------------|--------------|----------------|----------------|----------------|----------------|-------------|----------------|----------------|--------------|----------------|----------------|--------------|----------------|----------------|---------------|
| CS-5500E | 4.22 | 20.9 | 0.17 | 2.8 | 0.087 | 2.09 | 45.9 | 47.1 | 0.62 | 829 | 1.02 | 0.92 | 11 | 20 | 1500 |
| CS-6520E | 1.7 | 17.75 | 0.12 | 3.9 | 0.018 | 2.03 | 18.7 | 19.5 | 0.46 | 496 | 1.63 | 2.44 | 6.2 | 4.3 | 600 |
| CS-7540E | 3.14 | 19.4 | 0.2 | 3.5 | 0.042 | 2.02 | 38.7 | 43 | 0.58 | 608 | 1.23 | 1.61 | 9.7 | 16.1 | 960 |
| CS-8560E | 4.18 | 22.1 | 0.24 | 3.1 | 0.061 | 2.06 | 49.8 | 63.6 | 0.57 | 1090 | 0.98 | 0.95 | 11.1 | 24.5 | 2090 |
| CS-9580E | 1.65 | 17.4 | 0.16 | 4 | 0.017 | 2.03 | 17.1 | 18.8 | 0.49 | 334 | 1.5 | 2.57 | 6.1 | 3.7 | 810 |
| CS-10600E | 1.68 | 17.5 | 0.15 | 4.1 | 0.015 | 2.04 | 15.9 | 18.9 | 0.52 | 345 | 1.57 | 2.68 | 5.7 | 3.7 | 590 |
| CS-11620E | 3.76 | 21.4 | 0.24 | 3.4 | 0.057 | 2.13 | 59.5 | 56.7 | 0.7 | 688 | 0.96 | 1.23 | 12.6 | 25 | 870 |
| CS-12640E | 1.51 | 17.35 | 0.18 | 4.2 | 0.015 | 2.08 | 16.7 | 19.2 | 0.42 | 327 | 1.6 | 2.65 | 5.8 | 2.9 | 570 |
| CS-13650E | 4.89 | 24.7 | 0.29 | 3.2 | 0.073 | 2.23 | 75.5 | 75.8 | 0.87 | 982 | 0.9 | 0.82 | 14.6 | 38.9 | 760 |
| CS-14660E | 3.25 | 19 | 0.21 | 3.5 | 0.041 | 1.96 | 44.9 | 38.3 | 0.57 | 451 | 1.18 | 1.66 | 9.8 | 14.7 | 1140 |
| CS-15680E | 1.66 | 17.05 | 0.16 | 3.9 | 0.018 | 1.95 | 17.1 | 18.7 | 0.44 | 368 | 1.56 | 2.46 | 5.9 | 3.6 | 900 |
| CS-16700E | 5.39 | 23.9 | 0.26 | 3 | 0.073 | 2.11 | 75.4 | 66.6 | 0.8 | 977 | 0.79 | 0.61 | 13.3 | 33.1 | 1110 |
| CS-17720E | 2.16 | 18.55 | 0.13 | 3.2 | 0.027 | 2 | 25.7 | 32.1 | 0.52 | 388 | 1.53 | 2.26 | 7 | 8.8 | 730 |
| CS-18740E | 2.05 | 18.55 | 0.11 | 3.2 | 0.021 | 1.89 | 18.7 | 22.2 | 0.52 | 405 | 1.47 | 2.31 | 6.2 | 5.2 | 1100 |
| CS-19760E | 3.83 | 21.3 | 0.1 | 3.2 | 0.048 | 1.93 | 44.2 | 47.7 | 0.68 | 726 | 1.2 | 1.31 | 11.6 | 23.8 | 990 |
| C-S1 | 7.87 | 26.4 | 0.15 | 3.7 | 0.074 | 2.34 | 75.1 | 55 | 0.54 | 523 | 4.37 | 1.14 | 10.2 | 27 | 1340 |
| C-S2 | 5.23 | 26.3 | 0.15 | 3.3 | 0.086 | 2.62 | 62.7 | 80.8 | 0.87 | 951 | 1.3 | 0.85 | 12.1 | 46.2 | 1070 |
| C-S3 | 5.6 | 29.7 | 0.17 | 3.3 | 0.09 | 2.65 | 88 | 96.3 | 0.95 | 1005 | 0.91 | 0.59 | 14.9 | 48.3 | 690 |
| C-S4 | 5.98 | 24.5 | 0.16 | 2.7 | 0.074 | 2.38 | 71.4 | 76.1 | 0.72 | 816 | 0.94 | 0.45 | 12.9 | 32.1 | 1160 |
| C-A1S | 38.8 | 5.49 | 0.41 | 0.6 | 0.014 | 0.5 | 21.6 | 7.6 | 0.1 | 2250 | 0.27 | 0.17 | 2 | 4.9 | 530 |
| CR-A1 | 6.2 | 31.7 | 0.27 | 1.9 | 0.129 | 2.1 | 121.5 | 65.5 | 0.95 | 3320 | 0.39 | 0.74 | 5.5 | 41.5 | 660 |
| CR-A2 | 5.74 | 36.8 | 0.25 | 2.3 | 0.125 | 2.31 | 91.7 | 81.9 | 0.91 | 2400 | 0.5 | 0.76 | 6.5 | 48.7 | 550 |
| CR-A3 | 5.63 | 32.9 | 0.25 | 2.5 | 0.099 | 2.69 | 111.5 | 73.7 | 0.87 | 1560 | 0.61 | 0.64 | 9.7 | 50.4 | 680 |
| CR-A4 | 5.94 | 32.9 | 0.22 | 2.5 | 0.096 | 2.68 | 122.5 | 63.7 | 0.9 | 1730 | 0.59 | 0.65 | 10.5 | 50.7 | 760 |
| CR-A5 | 5.9 | 33.9 | 0.25 | 2.4 | 0.106 | 2.5 | 132.5 | 70.6 | 0.88 | 2050 | 0.58 | 0.63 | 10.2 | 50.2 | 770 |
| CR-A6 | 5.89 | 32.2 | 0.23 | 2.5 | 0.093 | 2.55 | 109.5 | 74.9 | 0.88 | 1680 | 0.57 | 0.68 | 10.6 | 50 | 810 |
| CR-A7 | 5.74 | 32.7 | 0.23 | 2.2 | 0.084 | 2.25 | 95.9 | 72.6 | 0.94 | 2040 | 0.48 | 0.8 | 8.8 | 45.9 | 680 |
| CR-27 | 1.85 | 14.8 | 0.1 | 1.9 | 0.029 | 1.44 | 27.9 | 32.1 | 0.39 | 601 | 1.41 | 0.77 | 7.5 | 22.8 | 2070 |
| CR-28 | 4.12 | 24.5 | 0.26 | 2.9 | 0.062 | 2.07 | 55.1 | 73.9 | 0.69 | 1060 | 0.88 | 0.97 | 11.9 | 37.2 | 2110 |
| CR-29 | 4.77 | 24.4 | 0.24 | 3.2 | 0.075 | 2.23 | 71.7 | 96.7 | 0.68 | 584 | 0.95 | 0.49 | 10.8 | 71.9 | 2380 |
| CR-30 | 4.17 | 22.3 | 0.21 | 3.1 | 0.078 | 1.96 | 65.3 | 93.2 | 0.56 | 588 | 1.12 | 0.58 | 8.6 | 88.6 | 2920 |
| CR-31 | 5.79 | 29.4 | 0.21 | 2.5 | 0.079 | 2.26 | 75.6 | 93.1 | 1.05 | 876 | 1.94 | 0.58 | 12.3 | 55.1 | 490 |
| CR-32 | 4.35 | 28.9 | 0.18 | 2.7 | 0.062 | 2.28 | 60.7 | 80.7 | 0.91 | 621 | 1.18 | 0.9 | 14.3 | 37.3 | 690 |
| CR-33 | 2.43 | 15.85 | 0.12 | 1.9 | 0.043 | 1.43 | 45.5 | 49.7 | 0.5 | 355 | 0.96 | 0.57 | 7.8 | 58.6 | 1670 |
| CR-34 | 5.04 | 25 | 0.15 | 3 | 0.061 | 2.29 | 57.1 | 83.4 | 1.06 | 657 | 0.72 | 0.55 | 16.6 | 82.8 | 840 |



ALS Chemex
EXCELLENCE IN ANALYTICAL CHEMISTRY
 ALS Canada Ltd.

212 Brooksbank Avenue
 North Vancouver BC V7J 2C1
 Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: LEE, GARY
 P.O. BOX 31800
 WHITEHORSE YT Y1A 6L3

Page: 2 - C
 Total # Pages: 2 (A - D)
 Plus Appendix Pages
 Finalized Date: 1-AUG-2008
 Account: LEEGAR

CERTIFICATE OF ANALYSIS VA08094695

| Method Analyte Units LOR | ME-MS61 Pb ppm | ME-MS61 Rb ppm | ME-MS61 Re ppm | ME-MS61 S % | ME-MS61 Sb ppm | ME-MS61 Sc ppm | ME-MS61 Se ppm | ME-MS61 Sn ppm | ME-MS61 Sr ppm | ME-MS61 Ta ppm | ME-MS61 Te ppm | ME-MS61 Th ppm | ME-MS61 Ti % | ME-MS61 Tl ppm | ME-MS61 U ppm |
|--------------------------|----------------|----------------|----------------|-------------|----------------|----------------|----------------|----------------|----------------|----------------|----------------|----------------|--------------|----------------|---------------|
| CS-5500E | 24.6 | 97.5 | <0.002 | 0.06 | 0.6 | 11.3 | 1 | 3 | 186 | 0.81 | 0.06 | 14 | 0.301 | 0.56 | 2.5 |
| CS-6520E | 12.3 | 54.1 | <0.002 | 0.03 | 0.45 | 4.1 | 1 | 0.8 | 493 | 0.71 | <0.05 | 5.6 | 0.208 | 0.28 | 2 |
| CS-7540E | 18.6 | 84.2 | <0.002 | 0.03 | 0.55 | 7.9 | 1 | 1.8 | 318 | 0.71 | <0.05 | 11.9 | 0.28 | 0.44 | 2.5 |
| CS-8560E | 24.9 | 102 | <0.002 | 0.08 | 0.55 | 12.1 | 1 | 3 | 196 | 0.8 | <0.05 | 16.7 | 0.304 | 0.61 | 3.4 |
| CS-9580E | 10 | 52.2 | <0.002 | 0.02 | 0.46 | 4.2 | 1 | 0.8 | 513 | 0.45 | <0.05 | 5.4 | 0.21 | 0.28 | 1.9 |
| CS-10600E | 10 | 49.4 | <0.002 | 0.02 | 0.43 | 4.2 | 1 | 0.7 | 544 | 0.44 | <0.05 | 5 | 0.212 | 0.28 | 1.9 |
| CS-11620E | 22.5 | 94.6 | <0.002 | 0.02 | 0.59 | 10.8 | 1 | 3 | 233 | 0.92 | <0.05 | 16.2 | 0.33 | 0.56 | 2.7 |
| CS-12640E | 9.6 | 51.7 | <0.002 | 0.02 | 0.45 | 3.4 | 1 | 0.7 | 514 | 0.44 | <0.05 | 5.2 | 0.185 | 0.28 | 2 |
| CS-13650E | 26.6 | 117.5 | <0.002 | 0.02 | 0.7 | 14.1 | 1 | 3.7 | 147 | 1.08 | 0.05 | 20.9 | 0.361 | 0.68 | 3.4 |
| CS-14660E | 17.5 | 81.8 | <0.002 | 0.03 | 0.53 | 7.4 | 1 | 1.9 | 321 | 0.72 | <0.05 | 11.7 | 0.277 | 0.41 | 2.5 |
| CS-15680E | 10.4 | 51.1 | <0.002 | 0.03 | 0.51 | 3.8 | 1 | 0.7 | 486 | 0.44 | <0.05 | 5.6 | 0.194 | 0.28 | 2 |
| CS-16700E | 28.4 | 116 | <0.002 | 0.03 | 0.66 | 13.7 | 1 | 3.4 | 110 | 0.98 | 0.05 | 20 | 0.334 | 0.65 | 3.2 |
| CS-17720E | 13 | 61 | <0.002 | 0.02 | 0.44 | 5.6 | 1 | 1.2 | 474 | 0.51 | <0.05 | 7.7 | 0.212 | 0.33 | 3.4 |
| CS-18740E | 10.4 | 52.2 | <0.002 | 0.03 | 0.42 | 5.1 | 1 | 0.8 | 490 | 0.46 | <0.05 | 5.9 | 0.216 | 0.28 | 2.1 |
| CS-19760E | 26.7 | 87.2 | <0.002 | 0.04 | 0.61 | 10.4 | 2 | 2.3 | 258 | 0.8 | 0.05 | 14.5 | 0.311 | 0.45 | 2.8 |
| C-S1 | 133 | 114 | <0.002 | 0.07 | 1.75 | 14.7 | 2 | 3 | 246 | 0.7 | 0.17 | 40.2 | 0.245 | 0.61 | 6.1 |
| C-S2 | 54.1 | 135 | <0.002 | 0.03 | 0.98 | 15.8 | 2 | 4.2 | 199.5 | 0.87 | 0.05 | 22.2 | 0.344 | 0.73 | 3.6 |
| C-S3 | 49.3 | 146 | <0.002 | 0.02 | 0.96 | 18.6 | 2 | 4.4 | 133.5 | 1.07 | 0.05 | 25.3 | 0.376 | 0.83 | 3.8 |
| C-S4 | 53.9 | 128 | <0.002 | 0.04 | 0.93 | 15.2 | 2 | 3.9 | 115.5 | 0.91 | <0.05 | 22.2 | 0.368 | 0.72 | 3 |
| C-A1S | 16.4 | 28.4 | <0.002 | 0.73 | 0.55 | 2.2 | 2 | 0.6 | 29.8 | 0.12 | 0.05 | 5.8 | 0.05 | 0.93 | 1.2 |
| CR-A1 | 29.4 | 96.1 | <0.002 | 0.01 | 0.53 | 16.9 | 1 | 2.1 | 170 | 0.38 | <0.05 | 32.7 | 0.167 | 0.57 | 2 |
| CR-A2 | 35.3 | 120 | <0.002 | <0.01 | 0.63 | 20.4 | 2 | 2.6 | 175 | 0.45 | <0.05 | 26 | 0.165 | 0.74 | 2.3 |
| CR-A3 | 28.3 | 142.5 | <0.002 | 0.02 | 0.51 | 20.5 | 2 | 2.7 | 147.5 | 0.69 | <0.05 | 32.3 | 0.249 | 0.72 | 2.9 |
| CR-A4 | 28.1 | 148 | <0.002 | 0.02 | 0.55 | 19.1 | 2 | 2.9 | 154.5 | 0.75 | <0.05 | 34.4 | 0.264 | 0.77 | 3.1 |
| CR-A5 | 27.3 | 132 | <0.002 | 0.01 | 0.53 | 20.7 | 2 | 2.5 | 147.5 | 0.7 | 0.05 | 37.2 | 0.259 | 0.67 | 3.1 |
| CR-A6 | 31.1 | 139.5 | <0.002 | 0.01 | 0.54 | 20.8 | 2 | 2.6 | 158.5 | 0.72 | <0.05 | 33.4 | 0.273 | 0.69 | 3.3 |
| CR-A7 | 30.5 | 126.5 | <0.002 | 0.01 | 0.41 | 19.9 | 2 | 2.2 | 181.5 | 0.6 | <0.05 | 28.8 | 0.243 | 0.61 | 2.5 |
| CR-27 | 14.8 | 68.9 | <0.002 | 0.18 | 0.35 | 9.5 | 3 | 1.9 | 179 | 0.52 | <0.05 | 8 | 0.204 | 0.34 | 9.5 |
| CR-28 | 24.7 | 114.5 | <0.002 | 0.08 | 0.63 | 15.6 | 2 | 3.3 | 209 | 0.83 | <0.05 | 19 | 0.306 | 0.64 | 4.6 |
| CR-29 | 46.1 | 123.5 | <0.002 | 0.1 | 1.04 | 18.6 | 3 | 2.9 | 132.5 | 0.73 | <0.05 | 24.4 | 0.284 | 0.67 | 5.6 |
| CR-30 | 43.7 | 110.5 | <0.002 | 0.12 | 0.9 | 17 | 3 | 2.6 | 159.5 | 0.62 | 0.05 | 23 | 0.232 | 0.62 | 5.9 |
| CR-31 | 33.6 | 128.5 | <0.002 | 0.38 | 0.95 | 20.4 | 2 | 3.1 | 120 | 0.85 | 0.05 | 19 | 0.315 | 0.69 | 4.1 |
| CR-32 | 29.7 | 128 | <0.002 | 0.05 | 0.49 | 19.7 | 3 | 4.1 | 174.5 | 0.98 | <0.05 | 17.6 | 0.368 | 0.66 | 27.6 |
| CR-33 | 27.5 | 76 | 0.002 | 0.21 | 0.47 | 11.6 | 6 | 2.3 | 168.5 | 0.53 | <0.05 | 13.2 | 0.214 | 0.4 | 72.2 |
| CR-34 | 33.2 | 117.5 | <0.002 | 0.04 | 0.89 | 19.9 | 2 | 2.8 | 112 | 1.1 | <0.05 | 17.7 | 0.446 | 0.6 | 3.9 |



ALS Chemex
 EXCELLENCE IN ANALYTICAL CHEMISTRY

ALS Canada Ltd.

212 Brooksbank Avenue
 North Vancouver BC V7J 2C1

Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: LEE, GARY
 P.O. BOX 31800
 WHITEHORSE YT Y1A 6L3

Page: 2 - D
 Total # Pages: 2 (A - D)
 Plus Appendix Pages
 Finalized Date: 1-AUG-2008
 Account: LEEGAR

CERTIFICATE OF ANALYSIS VA08094695

| Sample Description | Method Analyte Units LOR | ME-MS61 V ppm | ME-MS61 W ppm | ME-MS61 Y ppm | ME-MS61 Zn ppm | ME-MS61 Zr ppm |
|--------------------|--------------------------|---------------|---------------|---------------|----------------|----------------|
| CS-5500E | | 77 | 1.5 | 9.7 | 109 | 86 |
| CS-6520E | | 35 | 0.8 | 6.9 | 47 | 130 |
| CS-7540E | | 54 | 1.8 | 9.3 | 78 | 113 |
| CS-8560E | | 72 | 2 | 9.7 | 103 | 93.7 |
| CS-9580E | | 36 | 0.7 | 6.7 | 45 | 131.5 |
| CS-10600E | | 38 | 0.6 | 6.7 | 45 | 132.5 |
| CS-11620E | | 71 | 1.6 | 10.7 | 86 | 105.5 |
| CS-12640E | | 29 | 0.6 | 6.4 | 43 | 136.5 |
| CS-13650E | | 84 | 2.4 | 12.9 | 111 | 96.1 |
| CS-14660E | | 52 | 1.4 | 8.9 | 64 | 112 |
| CS-15680E | | 33 | 0.7 | 6.4 | 45 | 130 |
| CS-16700E | | 83 | 1.8 | 13 | 99 | 88.6 |
| CS-17720E | | 39 | 0.8 | 7.6 | 57 | 122.5 |
| CS-18740E | | 39 | 0.6 | 7 | 46 | 121.5 |
| CS-19760E | | 62 | 2 | 9.9 | 81 | 106.5 |
| C-S1 | | 71 | 1.8 | 18.4 | 129 | 117 |
| C-S2 | | 91 | 1.9 | 13.3 | 142 | 98.9 |
| C-S3 | | 93 | 1.6 | 21.6 | 138 | 96.3 |
| C-S4 | | 86 | 1.9 | 11.2 | 112 | 82.1 |
| C-A1S | | 19 | 0.6 | 7.4 | 115 | 17.5 |
| CR-A1 | | 89 | 0.8 | 8.1 | 139 | 54.5 |
| CR-A2 | | 89 | 4.2 | 7.8 | 126 | 67.4 |
| CR-A3 | | 109 | 0.9 | 10.4 | 123 | 79.1 |
| CR-A4 | | 112 | 1.1 | 10.9 | 128 | 79.2 |
| CR-A5 | | 108 | 1 | 11.4 | 133 | 80.2 |
| CR-A6 | | 111 | 1.1 | 11 | 125 | 84.1 |
| CR-A7 | | 93 | 0.9 | 8.5 | 131 | 70.5 |
| CR-27 | | 44 | 1 | 14.9 | 85 | 63.2 |
| CR-28 | | 77 | 2.1 | 17.1 | 160 | 98.7 |
| CR-29 | | 78 | 1.5 | 33.7 | 175 | 105.5 |
| CR-30 | | 69 | 1.2 | 37.1 | 179 | 101 |
| CR-31 | | 91 | 1.6 | 17.8 | 129 | 82.6 |
| CR-32 | | 92 | 1.8 | 18.4 | 165 | 89.2 |
| CR-33 | | 50 | 1.2 | 25 | 201 | 61.9 |
| CR-34 | | 97 | 1.6 | 19.5 | 157 | 96.8 |

CERTIFICATE OF ANALYSIS VA08094695

CERTIFICATE COMMENTS

Method

ME-MS61

REE's may not be totally soluble in this method.



ALS Chemex
EXCELLENCE IN ANALYTICAL CHEMISTRY

212 Brooksbank Avenue
 North Vancouver BC V7J 2C1
 Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: LEE, GARY
 P.O. BOX 31800
 WHITEHORSE YT Y1A 6L3

Page: 1
 Finalized Date: 12-OCT-2008
 This copy reported on 15-OCT-2008
 Account: LEEGAR

CERTIFICATE VA08137121

Project:
 P.O. No.:
 This report is for 7 Rock samples submitted to our lab in Vancouver, BC, Canada on 25-SEP-2008.
 The following have access to data associated with this certificate:


GARY LEE | BOB SCOTT

| SAMPLE PREPARATION | |
|--------------------|--------------------------------|
| ALS CODE | DESCRIPTION |
| WEI-21 | Received Sample Weight |
| LOG-22 | Sample login - Rcd w/o BarCode |
| CRU-31 | Fine crushing - 70% <2mm |
| SPL-21 | Split sample - riffle splitter |
| PUL-31 | Pulverize split to 85% <75 um |

| ANALYTICAL PROCEDURES | | |
|-----------------------|-------------------------------|------------|
| ALS CODE | DESCRIPTION | INSTRUMENT |
| ME-ICP41 | 35 Element Aqua Regia ICP-AES | ICP-AES |
| Au-ICP21 | Au 30g FA ICP-AES Finish | ICP-AES |

To: LEE, GARY
 P.O. BOX 31800
 WHITEHORSE YT Y1A 6L3

This is the Final Report and supersedes any preliminary report with this certificate number. Results apply to samples as submitted. All pages of this report have been checked and approved for release.

Signature: 
 Colin Ramshaw, Vancouver Laboratory Manager



ALS Chemex
EXCELLENCE IN ANALYTICAL CHEMISTRY

212 Brooksbank Avenue
 North Vancouver BC V7J 2C1
 Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: LEE, GARY
 P.O. BOX 31800
 WHITEHORSE YT Y1A 6L3

Page: 2 - A
 Total # Pages: 2 (A - C)
 Finalized Date: 12-OCT-2008
 Account: LEEGAR

CERTIFICATE OF ANALYSIS VA08137121

| Sample Description | Method Analyte Units LOR | ME-ICP41 | | | | | | | | | | | | | | ME-ICP41 | |
|--------------------|--------------------------|----------|--------|------|--------|-------|--------|--------|--------|------|--------|--------|--------|--------|------|----------|----------|
| | | Au ppm | Ag ppm | Al % | As ppm | B ppm | Ba ppm | Be ppm | Bi ppm | Ca % | Cd ppm | Co ppm | Cr ppm | Cu ppm | Fe % | Me-ICP41 | Me-ICP41 |
| C-RF6 | WEI-21 Recvd Wt. kg | 0.001 | <0.001 | 0.81 | 3 | <10 | 10 | <0.5 | <2 | 0.08 | <0.5 | 5 | 14 | 12 | 1.77 | | |
| C-RF7 | | 0.001 | 0.310 | 3.10 | 39 | <10 | 10 | <0.5 | <2 | 0.03 | <0.5 | 11 | 18 | 32 | 6.23 | | |
| C-RF8T | | 0.001 | 1.775 | 0.27 | 4090 | <10 | 50 | <0.5 | 2 | 0.03 | <0.5 | 1 | 10 | 11 | 1.57 | | |
| C-RF9T | | 0.001 | 6.34 | 0.51 | 6810 | <10 | 10 | <0.5 | 2 | 0.10 | <0.5 | 3 | 17 | 6 | 1.57 | | |
| C-RF10 | | 0.001 | 0.058 | 4.09 | 122 | <10 | 20 | <0.5 | 3 | 0.25 | <0.5 | 7 | 24 | 25 | 7.45 | | |
| CVRT49 | | 0.001 | 0.019 | 0.58 | 15 | <10 | <10 | <0.5 | <2 | 0.03 | <0.5 | 4 | 18 | 6 | 1.44 | | |
| WP17A | | 0.001 | 0.290 | 1.15 | 6910 | <10 | 40 | <0.5 | 2 | 0.02 | <0.5 | 13 | 16 | 17 | 3.45 | | |



ALS Chemex
EXCELLENCE IN ANALYTICAL CHEMISTRY

212 Brooksbank Avenue
 North Vancouver BC V7J 2C1
 Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: LEE, GARY
 P.O. BOX 31800
 WHITEHORSE YT Y1A 6L3

Page: 2 - B
 Total # Pages: 2 (A - C)
 Finalized Date: 12-OCT-2008
 Account: LEEGAR

CERTIFICATE OF ANALYSIS VA08137121

| Sample Description | Method Analyte Units LOR | ME-ICP41 | | | | | | | | | | | | | | |
|--------------------|--------------------------|----------|--------|------|--------|------|--------|--------|------|--------|-------|--------|-----|--------|--------|--------|
| | | Ga ppm | Hg ppm | K % | La ppm | Mg % | Mn ppm | Mo ppm | Na % | Ni ppm | P ppm | Pb ppm | S % | Sb ppm | Sc ppm | Sr ppm |
| C-RF6 | | <10 | <1 | 0.02 | <10 | 0.33 | 376 | <1 | 0.01 | 12 | 240 | 4 | <2 | 1 | 4 | |
| C-RF7 | | 10 | <1 | 0.03 | 10 | 1.41 | 1065 | <1 | 0.01 | 31 | 150 | 10 | <2 | 2 | 5 | |
| C-RF8T | | <10 | <1 | 0.09 | 10 | 0.05 | 61 | <1 | 0.01 | 5 | 140 | 50 | <2 | <1 | 11 | |
| C-RF9T | | <10 | <1 | 0.05 | <10 | 0.20 | 171 | <1 | 0.01 | 7 | 480 | 26 | 3 | 1 | 22 | |
| C-RF10 | | 10 | 1 | 0.09 | 20 | 1.94 | 1115 | <1 | 0.02 | 42 | 1260 | 12 | <2 | 3 | 18 | |
| CVRT49 | | <10 | <1 | 0.01 | <10 | 0.24 | 246 | <1 | 0.01 | 9 | 120 | <2 | <2 | 1 | 2 | |
| WP17A | | <10 | <1 | 0.11 | 10 | 0.29 | 537 | <1 | 0.03 | 19 | 270 | 28 | <2 | 2 | 22 | |



ALS Chemex
EXCELLENCE IN ANALYTICAL CHEMISTRY

ALS Canada Ltd.
 212 Brooksbank Avenue
 North Vancouver BC V7J 2C1
 Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: LEE, GARY
 P.O. BOX 31800
 WHITEHORSE YT Y1A 6L3

Page: 2 - C
 Total # Pages: 2 (A - C)
 Finalized Date: 12-OCT-2008
 Account: LEEGAR

CERTIFICATE OF ANALYSIS VA08137121

| Sample Description | Method Analyte Units LOR | ME-ICP41 Th ppm 20 | ME-ICP41 Ti % 0.01 | ME-ICP41 Ti ppm 10 | ME-ICP41 U ppm 10 | ME-ICP41 V ppm 1 | ME-ICP41 W ppm 10 | ME-ICP41 Zn ppm 2 |
|--------------------|--------------------------|--------------------|--------------------|--------------------|-------------------|------------------|-------------------|-------------------|
| C-RF6 | | <20 | <0.01 | <10 | <10 | 7 | <10 | 41 |
| C-RF7 | | <20 | 0.01 | <10 | <10 | 27 | <10 | 145 |
| C-RF8T | | <20 | <0.01 | <10 | <10 | 3 | <10 | 14 |
| C-RF9T | | <20 | <0.01 | <10 | <10 | 4 | <10 | 20 |
| C-RF10 | | <20 | 0.01 | <10 | <10 | 31 | <10 | 158 |
| CVRT49 | | <20 | <0.01 | <10 | <10 | 5 | <10 | 27 |
| WP17A | | <20 | <0.01 | <10 | <10 | 10 | <10 | 57 |



ALS Chemex

EXCELLENCE IN ANALYTICAL CHEMISTRY

ALS Canada Ltd.
212 Brooksbank Avenue
North Vancouver BC V7J 2C1
Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: LEE, GARY
P.O. BOX 31800
WHITEHORSE YT Y1A 6L3

Page: 1
Finalized Date: 10-OCT-2008
This copy reported on 15-OCT-2008
Account: LEEGAR

CERTIFICATE VA08137122

Project:

P.O. No.:

This report is for 9 Soil samples submitted to our lab in Vancouver, BC, Canada on 25-SEP-2008.

The following have access to data associated with this certificate:

GARY LEE

BOB SCOTT

SAMPLE PREPARATION

| ALS CODE | DESCRIPTION |
|----------|--------------------------------|
| WEI-21 | Received Sample Weight |
| LOG-22 | Sample login - Rcd w/o BarCode |
| SCR-41 | Screen to -180um and save both |

ANALYTICAL PROCEDURES

| ALS CODE | DESCRIPTION | INSTRUMENT |
|----------|-------------------------------|------------|
| AU-ICP21 | Au 30g FA ICP-AES Finish | ICP-AES |
| ME-ICP41 | 35 Element Aqua Regia ICP-AES | ICP-AES |

To: LEE, GARY
P.O. BOX 31800
WHITEHORSE YT Y1A 6L3

This is the Final Report and supersedes any preliminary report with this certificate number. Results apply to samples as submitted. All pages of this report have been checked and approved for release.

Signature:

Colin Ramshaw, Vancouver Laboratory Manager



ALS Chemex
 EXCELLENCE IN ANALYTICAL CHEMISTRY

212 Brooksbank Avenue
 North Vancouver BC V7J 2C1
 Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: LEE, GARY
 P.O. BOX 31800
 WHITEHORSE YT Y1A 6L3

Page: 2 - A
 Total # Pages: 2 (A - C)
 Finalized Date: 10-OCT-2008
 Account: LEEGAR

CERTIFICATE OF ANALYSIS VA08137122

| Method Analyte Units LOR | Sample Description | WEI-21 Recvd Wt kg | Au-ICP21 Au ppm | ME-ICP41 Ag ppm | ME-ICP41 Al % | ME-ICP41 As ppm | ME-ICP41 B ppm | ME-ICP41 Ba ppm | ME-ICP41 Be ppm | ME-ICP41 Bi ppm | ME-ICP41 Ca % | ME-ICP41 Cd ppm | ME-ICP41 Co ppm | ME-ICP41 Cr ppm | ME-ICP41 Cu ppm | ME-ICP41 Fe % |
|--------------------------|--------------------|--------------------|-----------------|-----------------|---------------|-----------------|----------------|-----------------|-----------------|-----------------|---------------|-----------------|-----------------|-----------------|-----------------|---------------|
| C-S20770 | | 0.28 | 0.004 | <0.2 | 0.43 | <2 | <10 | 20 | <0.5 | <2 | 0.03 | <0.5 | 2 | 5 | 6 | 0.81 |
| C-S21780 | | 0.32 | 0.002 | 0.2 | 1.17 | 9 | <10 | 30 | <0.5 | <2 | 0.09 | <0.5 | 10 | 17 | 14 | 2.90 |
| C-S22800 | | 0.56 | 0.004 | <0.2 | 2.30 | 23 | <10 | 20 | <0.5 | 3 | 0.14 | <0.5 | 14 | 32 | 26 | 5.13 |
| C-S23820 | | 0.26 | 0.007 | <0.2 | 1.01 | 3 | <10 | 20 | <0.5 | <2 | 0.02 | <0.5 | 5 | 11 | 13 | 1.90 |
| C-S24630 | | 0.40 | 0.069 | 0.2 | 1.80 | 38 | <10 | 40 | <0.5 | 3 | 0.02 | <0.5 | 16 | 28 | 26 | 4.93 |
| C-S25640 | | 0.30 | 0.244 | <0.2 | 2.18 | 101 | <10 | 30 | <0.5 | 2 | 0.01 | <0.5 | 15 | 32 | 32 | 5.54 |
| C-S26650 | | 0.26 | 0.054 | 0.3 | 1.29 | 110 | <10 | 30 | <0.5 | <2 | 0.04 | <0.5 | 14 | 24 | 22 | 3.68 |
| C-27S660 | | 0.42 | 0.201 | <0.2 | 1.86 | 203 | <10 | 30 | <0.5 | <2 | 0.02 | <0.5 | 11 | 26 | 26 | 5.18 |
| C-28S670 | | 0.38 | 0.028 | <0.2 | 1.88 | 107 | <10 | 40 | <0.5 | <2 | 0.02 | <0.5 | 10 | 27 | 24 | 5.20 |



ALS Chemex
EXCELLENCE IN ANALYTICAL CHEMISTRY

ALS Canada Ltd.
 212 Brooksbank Avenue
 North Vancouver BC V7J 2C1
 Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: LEE, GARY
 P.O. BOX 31800
 WHITEHORSE YT Y1A 6L3

Page: 2 - B
 Total # Pages: 2 (A - C)
 Finalized Date: 10-OCT-2008
 Account: LEEGAR

CERTIFICATE OF ANALYSIS VA08137122

| Method Analyte Units LOR | ME-ICP41 | ME-ICP41 | ME-ICP41 | ME-ICP41 | ME-ICP41 | ME-ICP41 | ME-ICP41 | ME-ICP41 | ME-ICP41 | ME-ICP41 | ME-ICP41 | ME-ICP41 | ME-ICP41 | ME-ICP41 | ME-ICP41 | ME-ICP41 | ME-ICP41 | ME-ICP41 | ME-ICP41 |
|--------------------------|----------|----------|----------|----------|----------|----------|----------|----------|----------|----------|----------|----------|----------|----------|----------|----------|----------|----------|----------|
| Sample Description | Ga ppm | Hg ppm | K % | La ppm | Mg % | Mn ppm | Mo ppm | Na % | Ni ppm | P ppm | Pb ppm | S % | Sb ppm | Sc ppm | Sr ppm | | | | |
| C-S20770 | <10 | <1 | 0.02 | <10 | 0.05 | 176 | <1 | 0.01 | 3 | 490 | 5 | 0.06 | <2 | <1 | 4 | | | | |
| C-S21780 | 10 | <1 | 0.03 | 10 | 0.29 | 750 | <1 | <0.01 | 14 | 850 | 13 | 0.06 | <2 | <1 | 9 | | | | |
| C-S22800 | 10 | <1 | 0.02 | 30 | 0.79 | 636 | <1 | <0.01 | 27 | 530 | 15 | 0.03 | <2 | <1 | 12 | | | | |
| C-S23820 | <10 | 1 | 0.02 | 10 | 0.12 | 319 | <1 | 0.01 | 7 | 720 | 11 | 0.04 | <2 | <1 | 4 | | | | |
| C-S24630 | 10 | <1 | 0.03 | 20 | 0.38 | 1675 | <1 | <0.01 | 19 | 1780 | 40 | 0.04 | <2 | <1 | 6 | | | | |
| C-S25640 | 10 | 1 | 0.02 | 30 | 0.62 | 847 | <1 | <0.01 | 25 | 1150 | 14 | 0.03 | <2 | <1 | 5 | | | | |
| C-S26650 | 10 | <1 | 0.03 | 10 | 0.30 | 871 | <1 | <0.01 | 17 | 1320 | 15 | 0.05 | <2 | <1 | 7 | | | | |
| C-27S660 | 10 | <1 | 0.03 | 10 | 0.36 | 997 | <1 | <0.01 | 16 | 1870 | 20 | 0.06 | <2 | <1 | 5 | | | | |
| C-28S670 | 10 | <1 | 0.03 | 20 | 0.43 | 878 | <1 | <0.01 | 19 | 1190 | 16 | 0.04 | <2 | <1 | 4 | | | | |



ALS Chemex
EXCELLENCE IN ANALYTICAL CHEMISTRY

ALS Canada Ltd.
 212 Brooksbank Avenue
 North Vancouver BC V7J 2C1
 Phone: 604 984 0221 Fax: 604 984 0218 www.alschemex.com

To: LEE, GARY
 P.O. BOX 31800
 WHITEHORSE YT Y1A 6L3

Page: 2 - C
 Total # Pages: 2 (A - C)
 Finalized Date: 10-OCT-2008
 Account: LEEGAR

CERTIFICATE OF ANALYSIS VA08137122

| Sample Description | Method Analyte Units LOR | ME-ICP41 | | | | | | | | | | |
|--------------------|--------------------------|----------|------|--------|-------|-------|-------|--------|--------|--------|--------|-----|
| | | Th ppm | Ti % | Ti ppm | U ppm | V ppm | W ppm | Zn ppm | Zn ppm | Zn ppm | Zn ppm | |
| C-S20770 | | <20 | 0.01 | <10 | <10 | 10 | 1 | <10 | <10 | 10 | 2 | 17 |
| C-S21780 | | <20 | 0.01 | <10 | <10 | 17 | 17 | <10 | <10 | 10 | 10 | 59 |
| C-S22800 | | <20 | 0.01 | <10 | <10 | 20 | 20 | <10 | <10 | 10 | 10 | 100 |
| C-S23820 | | <20 | 0.01 | <10 | <10 | 17 | 17 | <10 | <10 | 10 | 10 | 27 |
| C-S24630 | | <20 | 0.02 | <10 | <10 | 29 | 29 | <10 | <10 | 10 | 10 | 73 |
| C-S25640 | | <20 | 0.01 | <10 | <10 | 27 | 27 | <10 | <10 | 10 | 10 | 99 |
| C-S26650 | | <20 | 0.01 | <10 | <10 | 21 | 21 | <10 | <10 | 10 | 10 | 77 |
| C-27S660 | | <20 | 0.01 | <10 | <10 | 27 | 27 | <10 | <10 | 10 | 10 | 86 |
| C-28S670 | | <20 | 0.01 | <10 | <10 | 28 | 28 | <10 | <10 | 10 | 10 | 83 |




APPENDIX VI

CREW LOG




Culvert Property
2008 Exploration Program Crew Log

| Date | Log |
|--------------|---|
| May 31 | Gary Lee and Ron Stack mobilize to property |
| June 1 | Camp set up |
| June 2 | Prospect and sampling |
| June 3 | Gary stakes more claims, Ron prospects |
| June 4 | Gary stakes more claims, Ron prospects |
| June 5 | Gary stakes more claims, Ron prospects |
| June 6 | Gary stakes more claims, Ron prospects |
| June 7 | Gary and Ron prospecting and sampling |
| June 8 | Gary stakes more claims, Ron prospects |
| June 9 | Both prospecting |
| June 10 | Both prospecting |
| June 11 | Gary stakes more claims, Ron prospects |
| June 12 | Gary stakes more claims, Ron prospects |
| June 13 | Both prospecting |
| June 14 | Gary stakes more claims, Ron prospects |
| June 15 | Both prospecting |
| June 16 | Demobilize to Watson Lake |
| June 17 – 21 | No work on property |
| June 22 | Gary and Ron return to property |
| June 23 | Work on ATV trail |


- June 24 Gary and Ron prospect and sample
- June 25 Both prospect and sample
- June 26 Both prospect and sample
- June 27 Both prospect and sample
- June 28 Both prospect and collect soil samples
- June 29 Gary stakes more claims, Ron prospects
- June 30 Tear down camp and demobilize to Watson Lake
- July 1 Drive to Whitehorse
- July 2 – August 29 No work on property
- Aug 30 Gary Lee mobilizes to Watson Lake
- Aug 31 Gary mobilizes to property and st-up camp
- Sept 1-9 Work on ATV trail
- Sept 10 Prospecting and sampling
- Sept 11 Work on ATV trail
- Sept 12 Work on ATV trail
- Sept 13 Prospecting and sampling
- Sept 14 Work on ATV trail
- Sept 15 - 20 Prospecting and sampling
- Sept 21 Tear down camp and demobilize to Watson Lake
- Sept 22 Spend day in Watson Lake organizing samples, logging rock chips and shipping samples.
- Sept 23 Return to Whitehorse

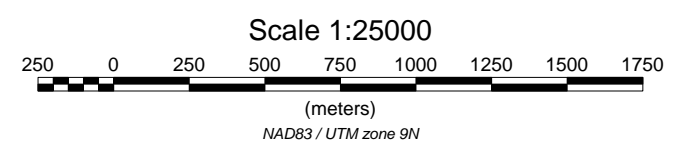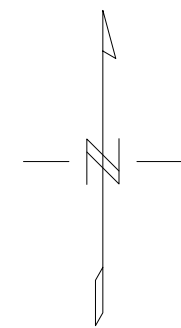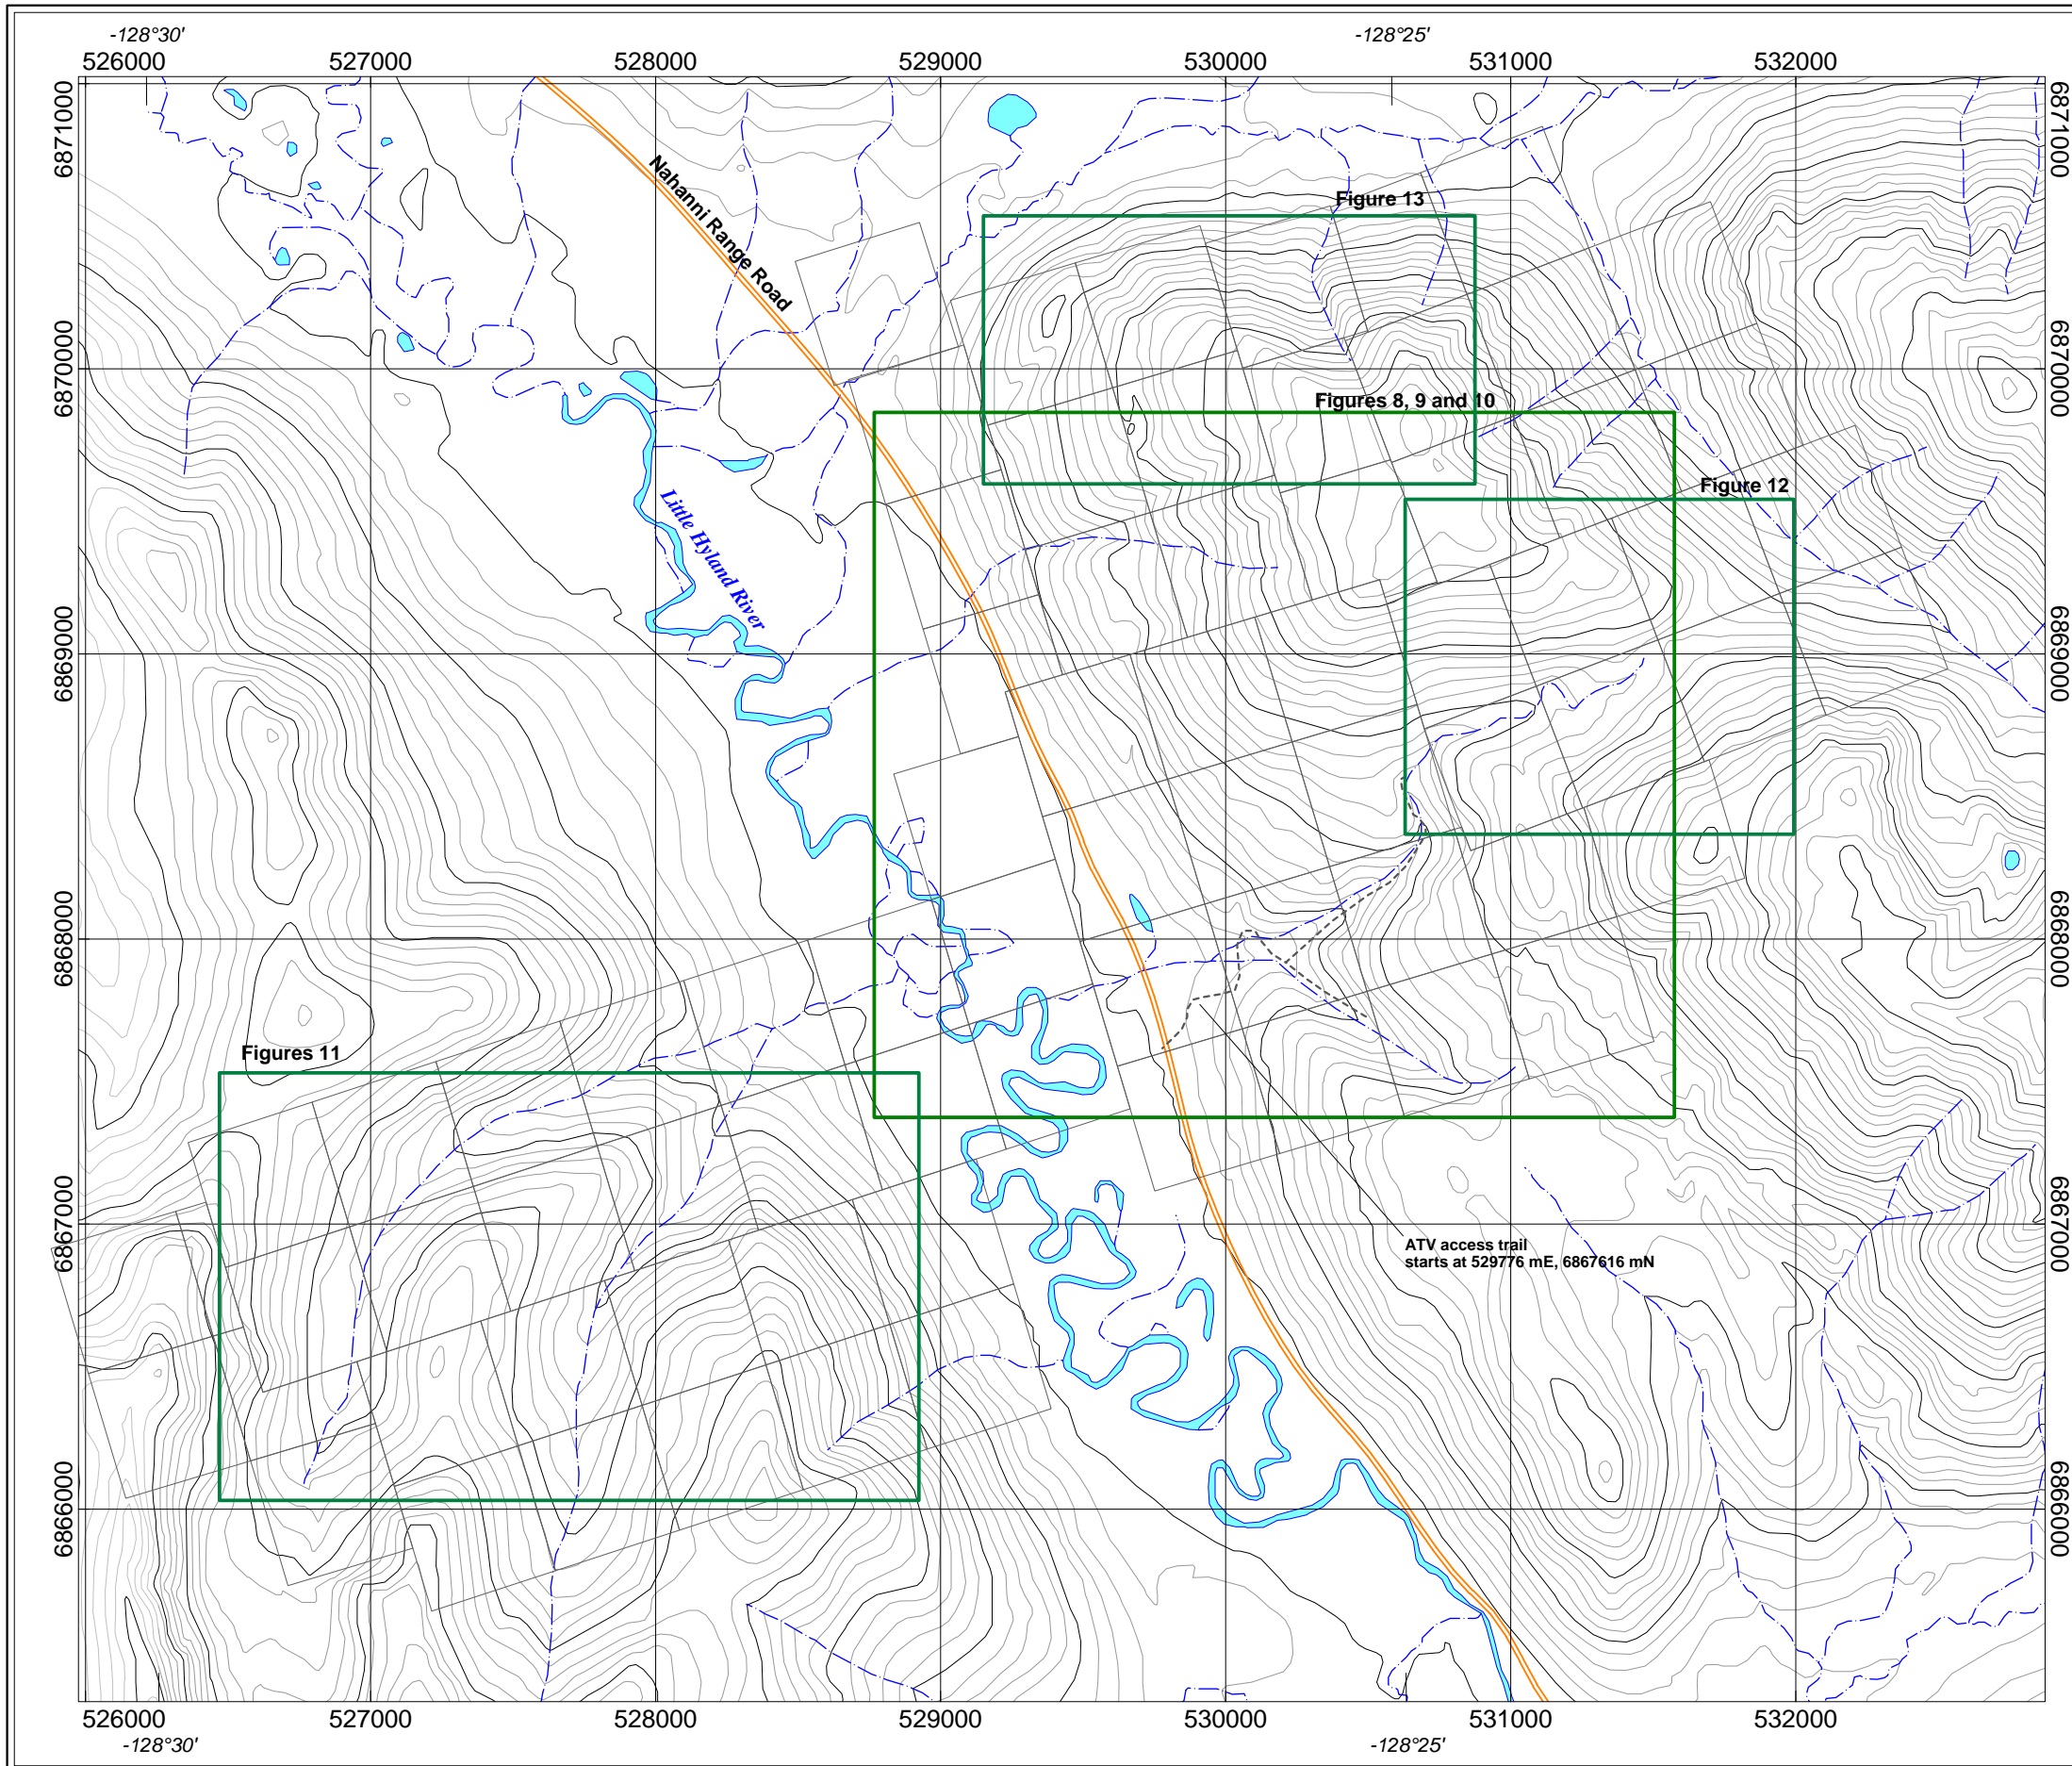

| | |
|--|------------------------------|
| GARY LEE | |
| GOLDEN CULVERT PROPERTY Figure 4. INDEX MAP | |
| NTS: 105H16 | Mining District: Watson Lake |
| DATUM: NAD83 | PROJECTION: UTM, zone 9 |
| Date: December 16, 2008 | |
| CASSELMAN GEOLOGICAL SERVICES Ltd | |

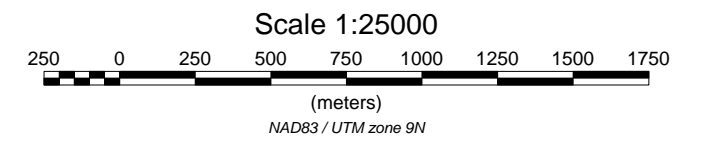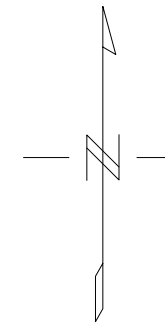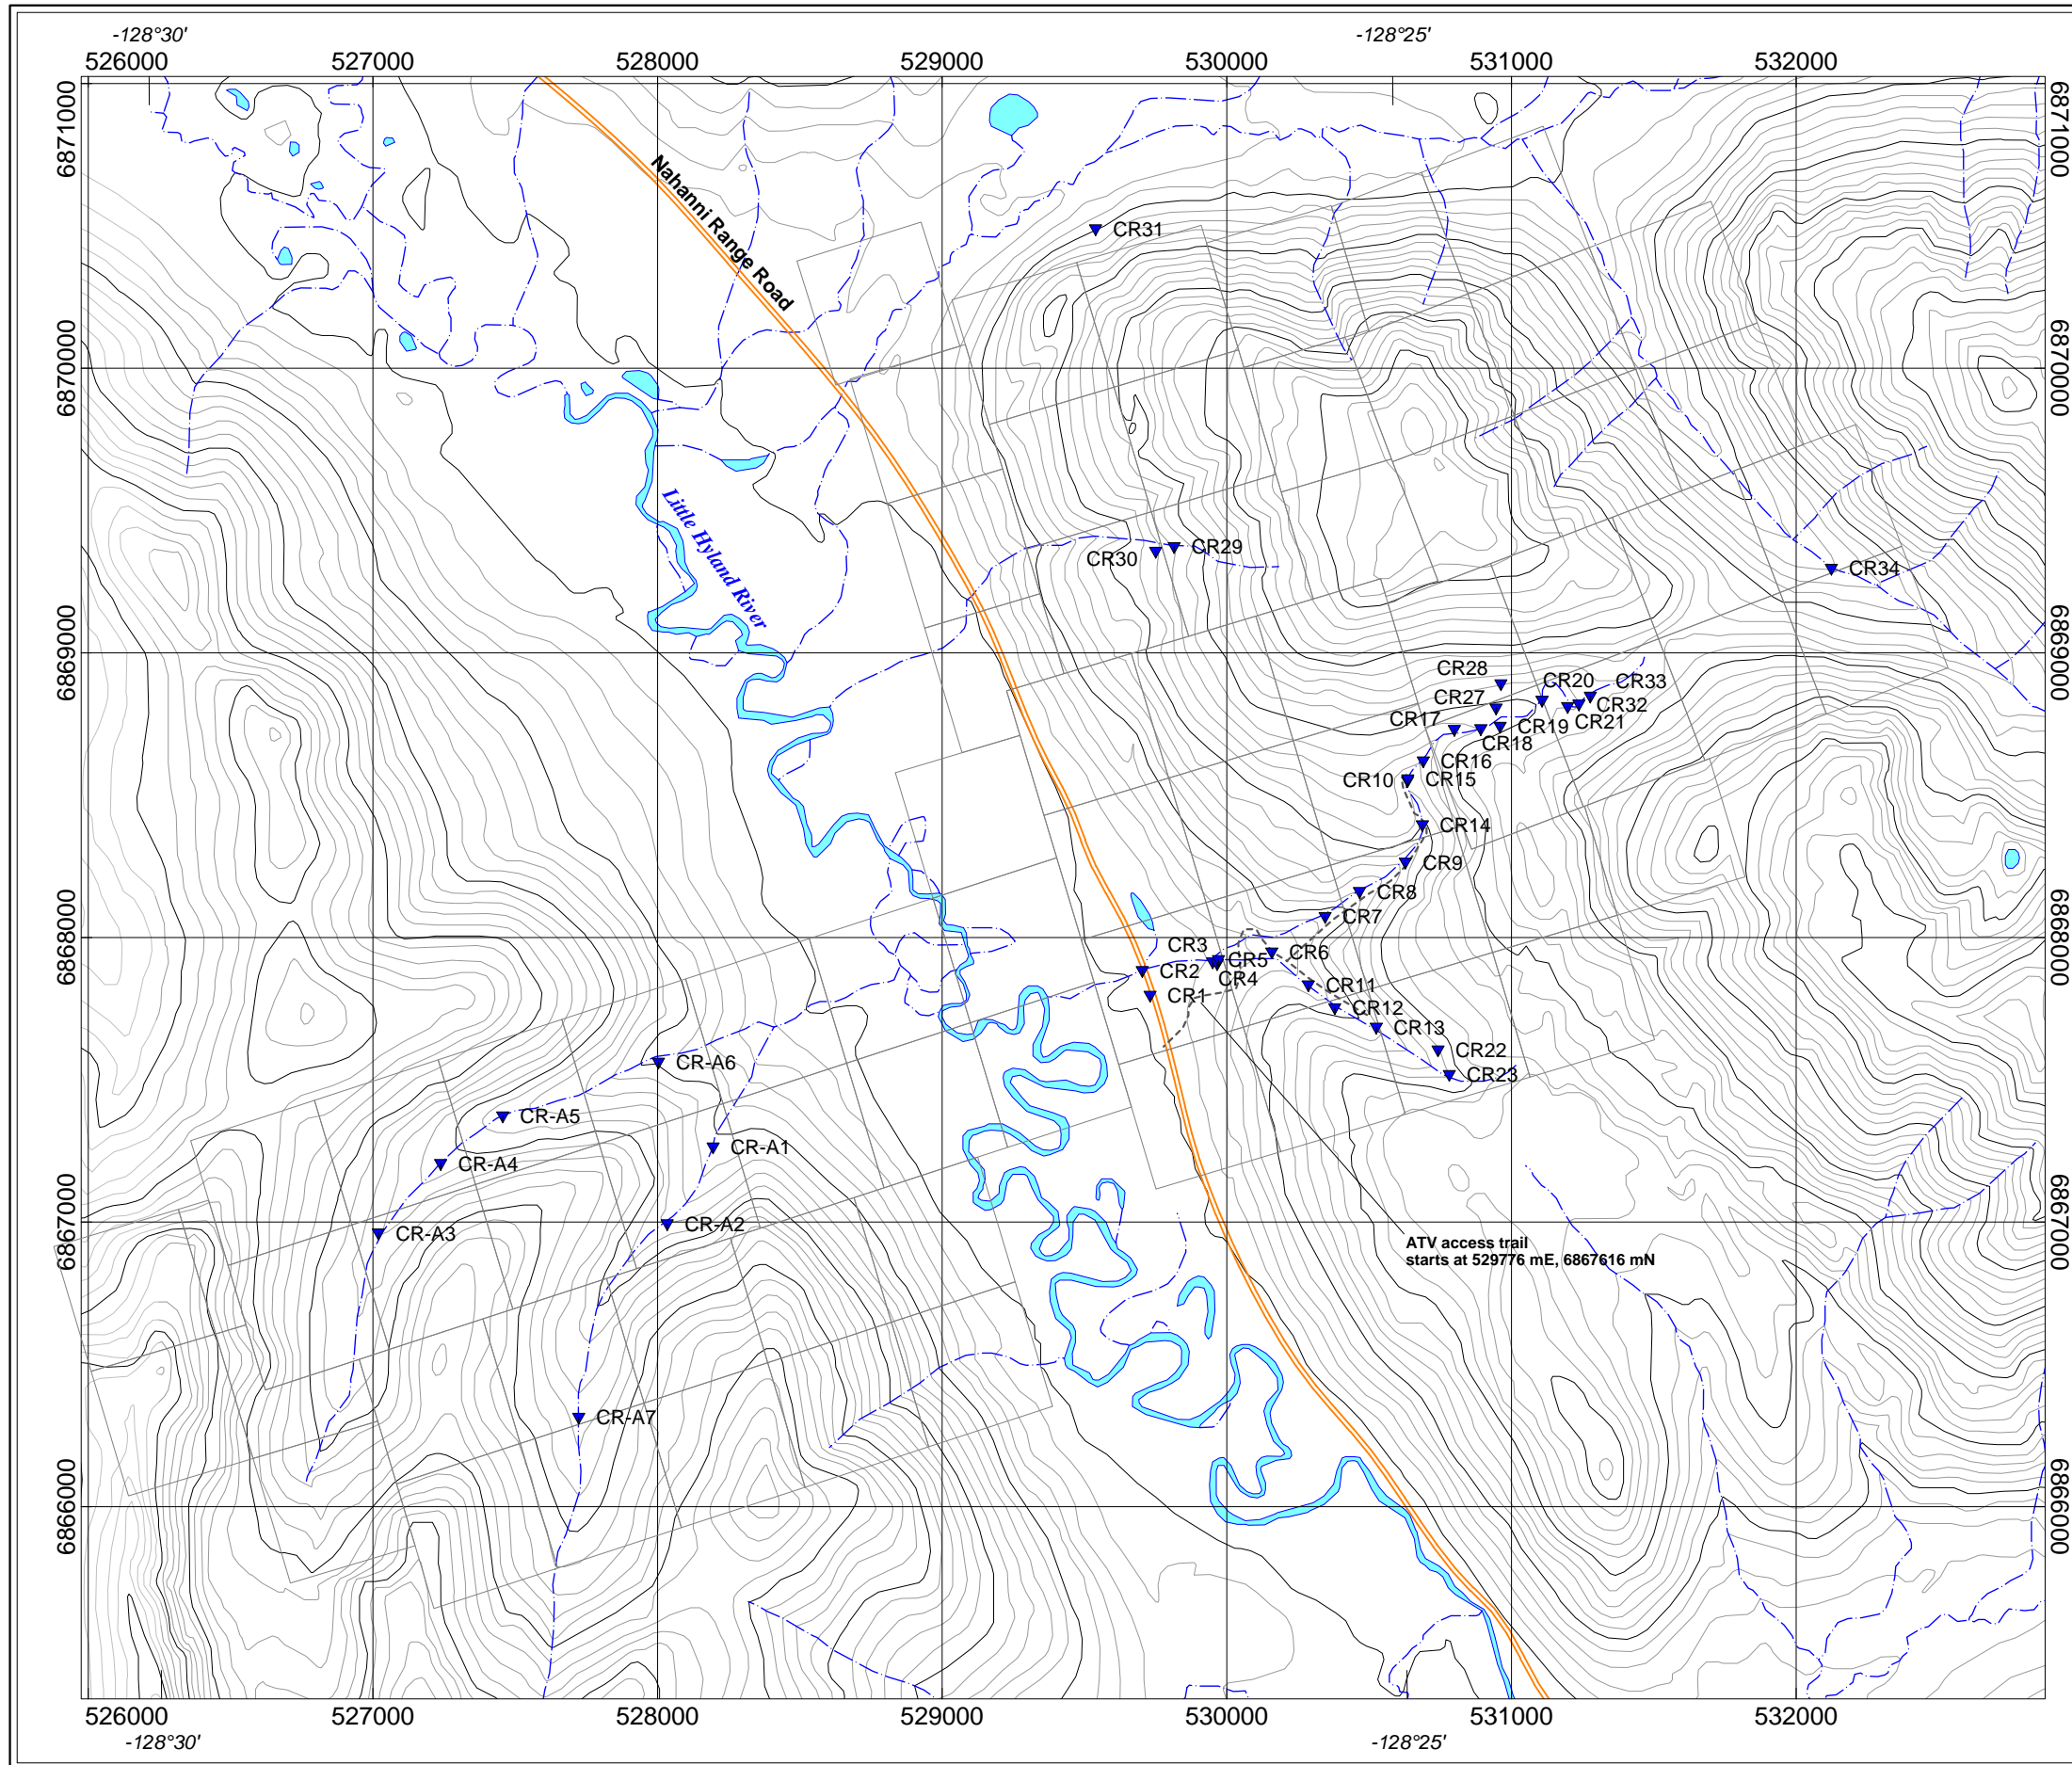

| | |
|---|------------------------------|
| GARY LEE | |
| GOLDEN CULVERT PROPERTY | |
| Figure 5 - Stream Sediment Sample Location Map | |
| NTS: 105H16 | Mining District: Watson Lake |
| DATUM: NAD83 | PROJECTION: UTM, zone 9 |
| Date: December 16, 2008 | |
| CASSELMAN GEOLOGICAL SERVICES Ltd | |




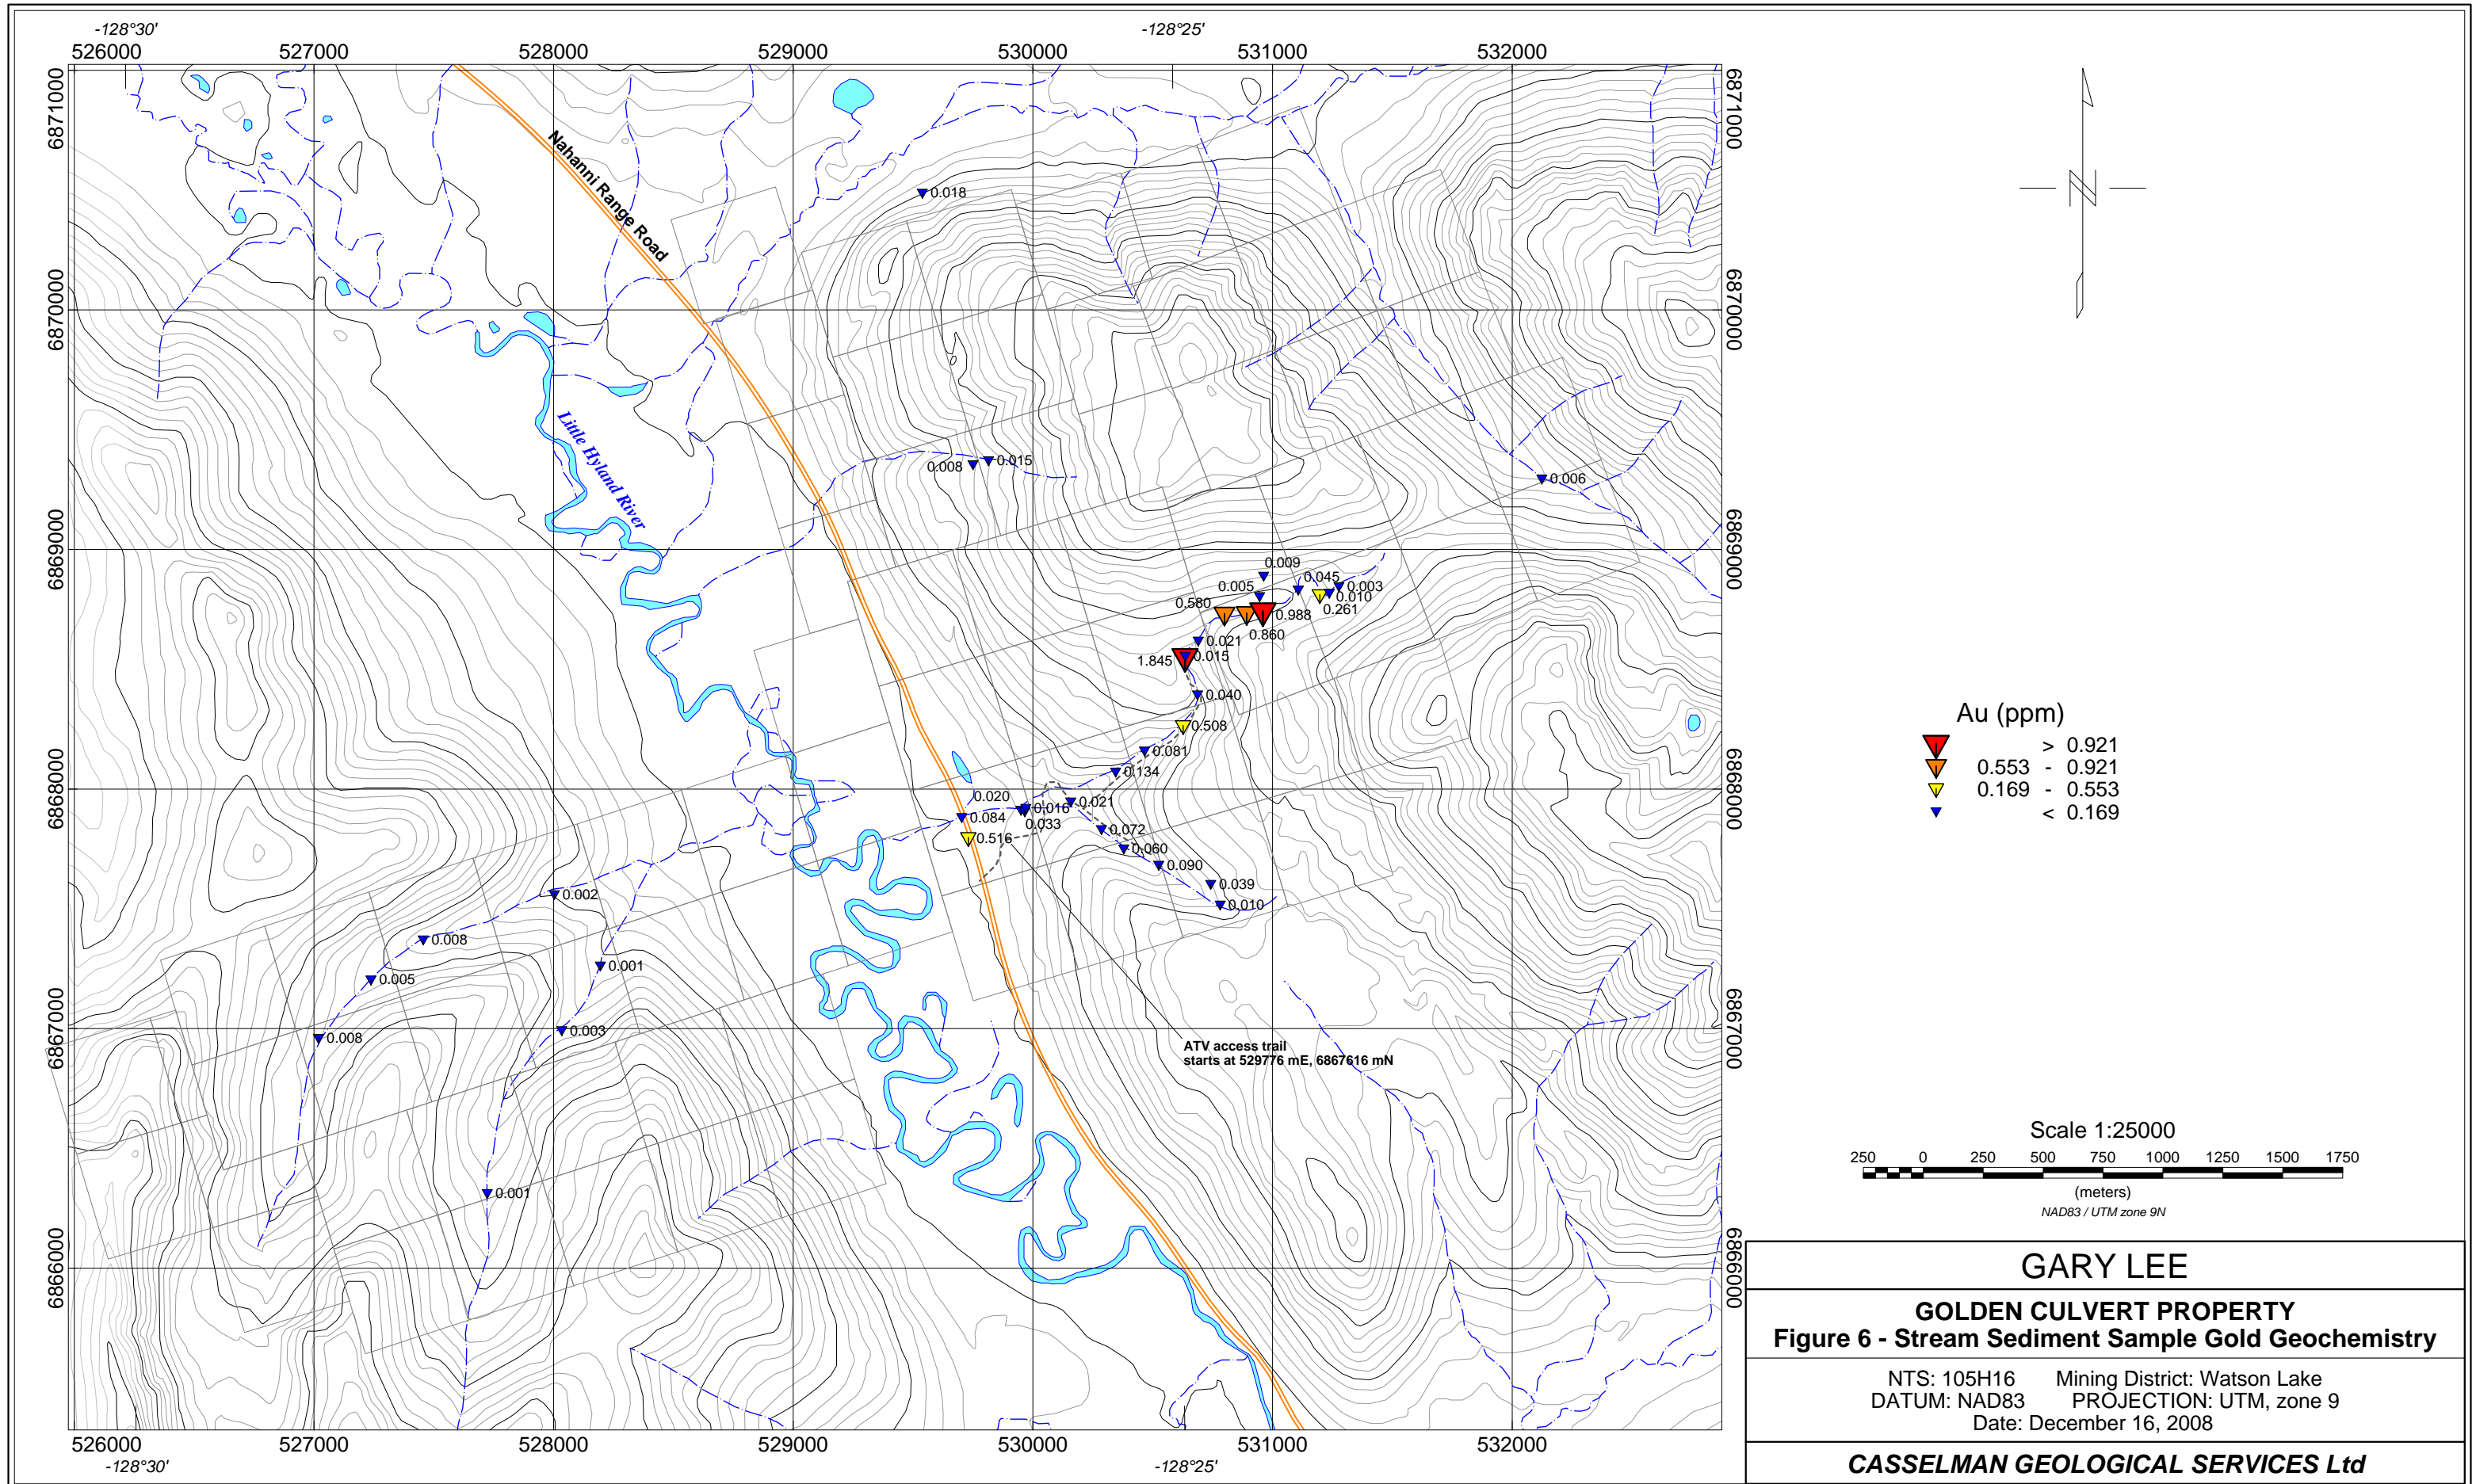


Au (ppm)


- ▼ (Red) > 0.921
- ▼ (Orange) 0.553 - 0.921
- ▼ (Yellow) 0.169 - 0.553
- ▼ (Blue) < 0.169


Scale 1:25000
 250 0 250 500 750 1000 1250 1500 1750
 (meters)
 NAD83 / UTM zone 9N


| |
|---|
| GARY LEE |
| GOLDEN CULVERT PROPERTY |
| Figure 6 - Stream Sediment Sample Gold Geochemistry |
| NTS: 105H16 Mining District: Watson Lake DATUM: NAD83 PROJECTION: UTM, zone 9 Date: December 16, 2008 |
| CASSELMAN GEOLOGICAL SERVICES Ltd |

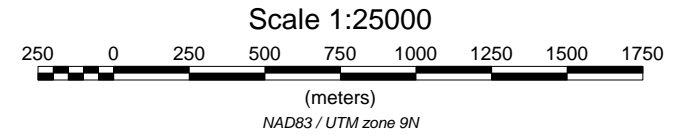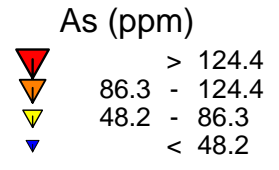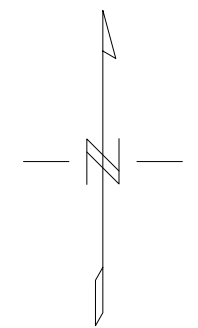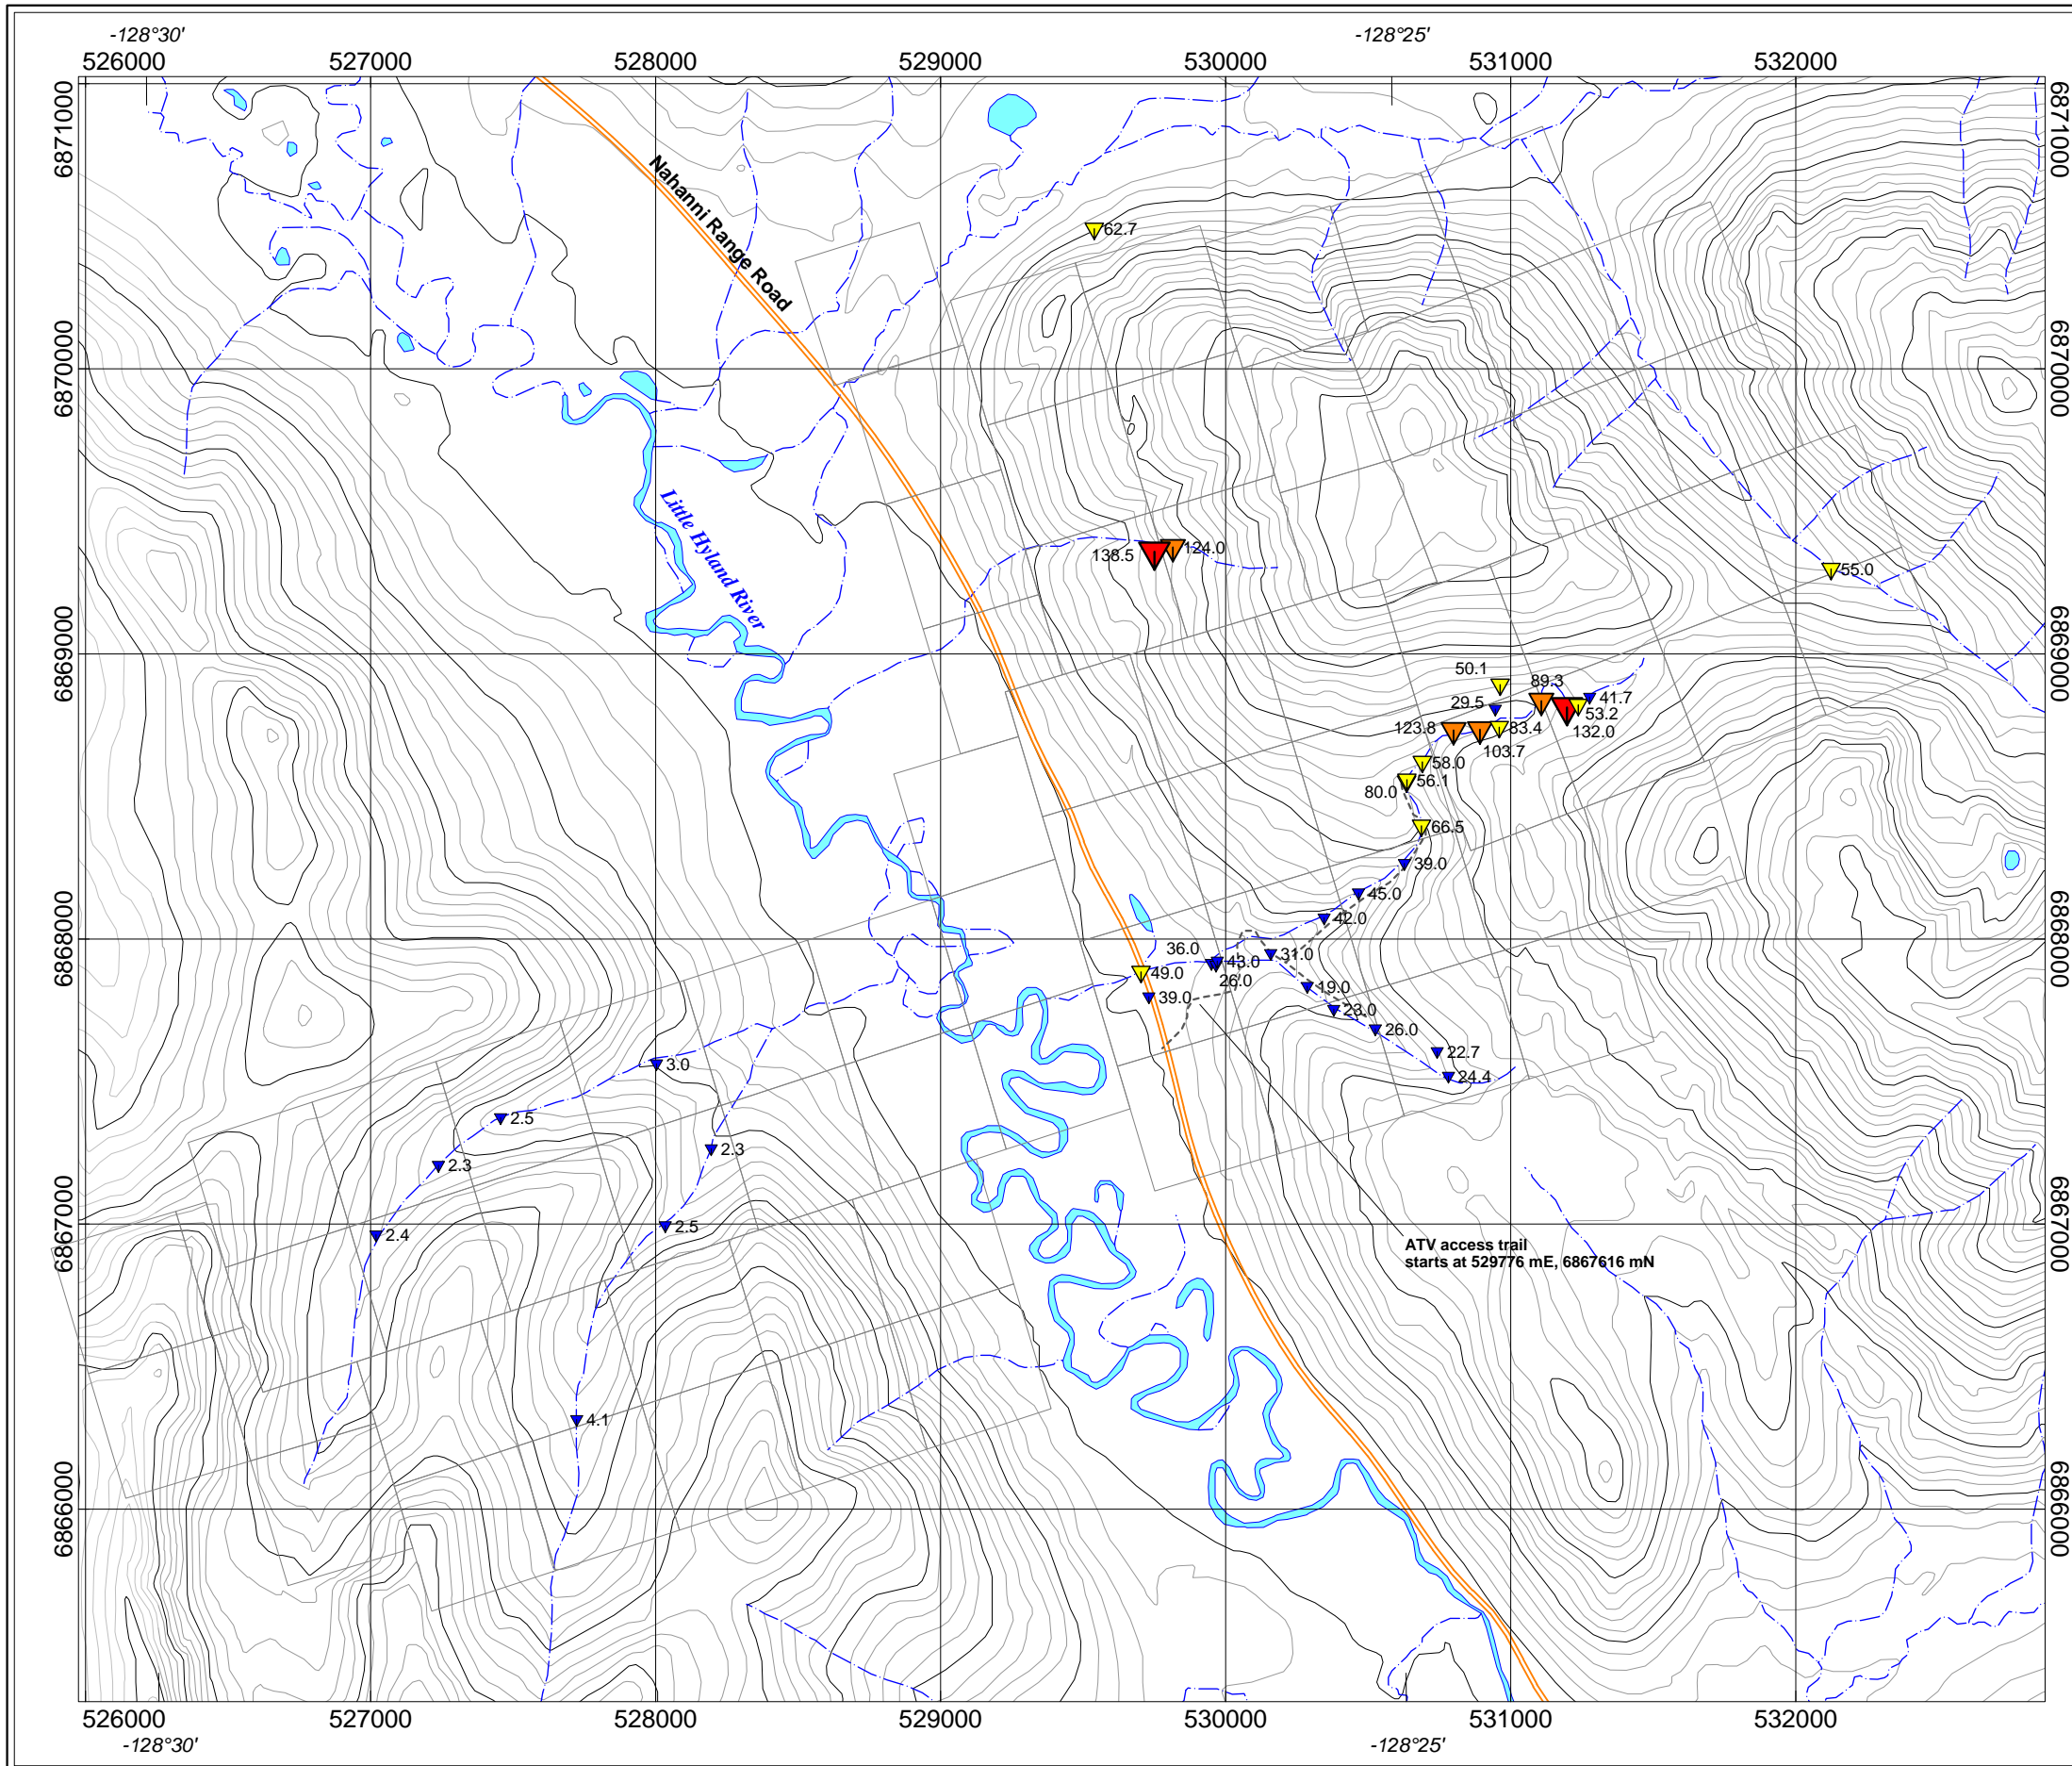

| | |
|---|------------------------------|
| GARY LEE | |
| GOLDEN CULVERT PROPERTY | |
| Figure 7 - Stream Sediment Sample Arsenic Geochemistry | |
| NTS: 105H16 | Mining District: Watson Lake |
| DATUM: NAD83 | PROJECTION: UTM, zone 9 |
| Date: December 16, 2008 | |
| CASSELMAN GEOLOGICAL SERVICES Ltd | |

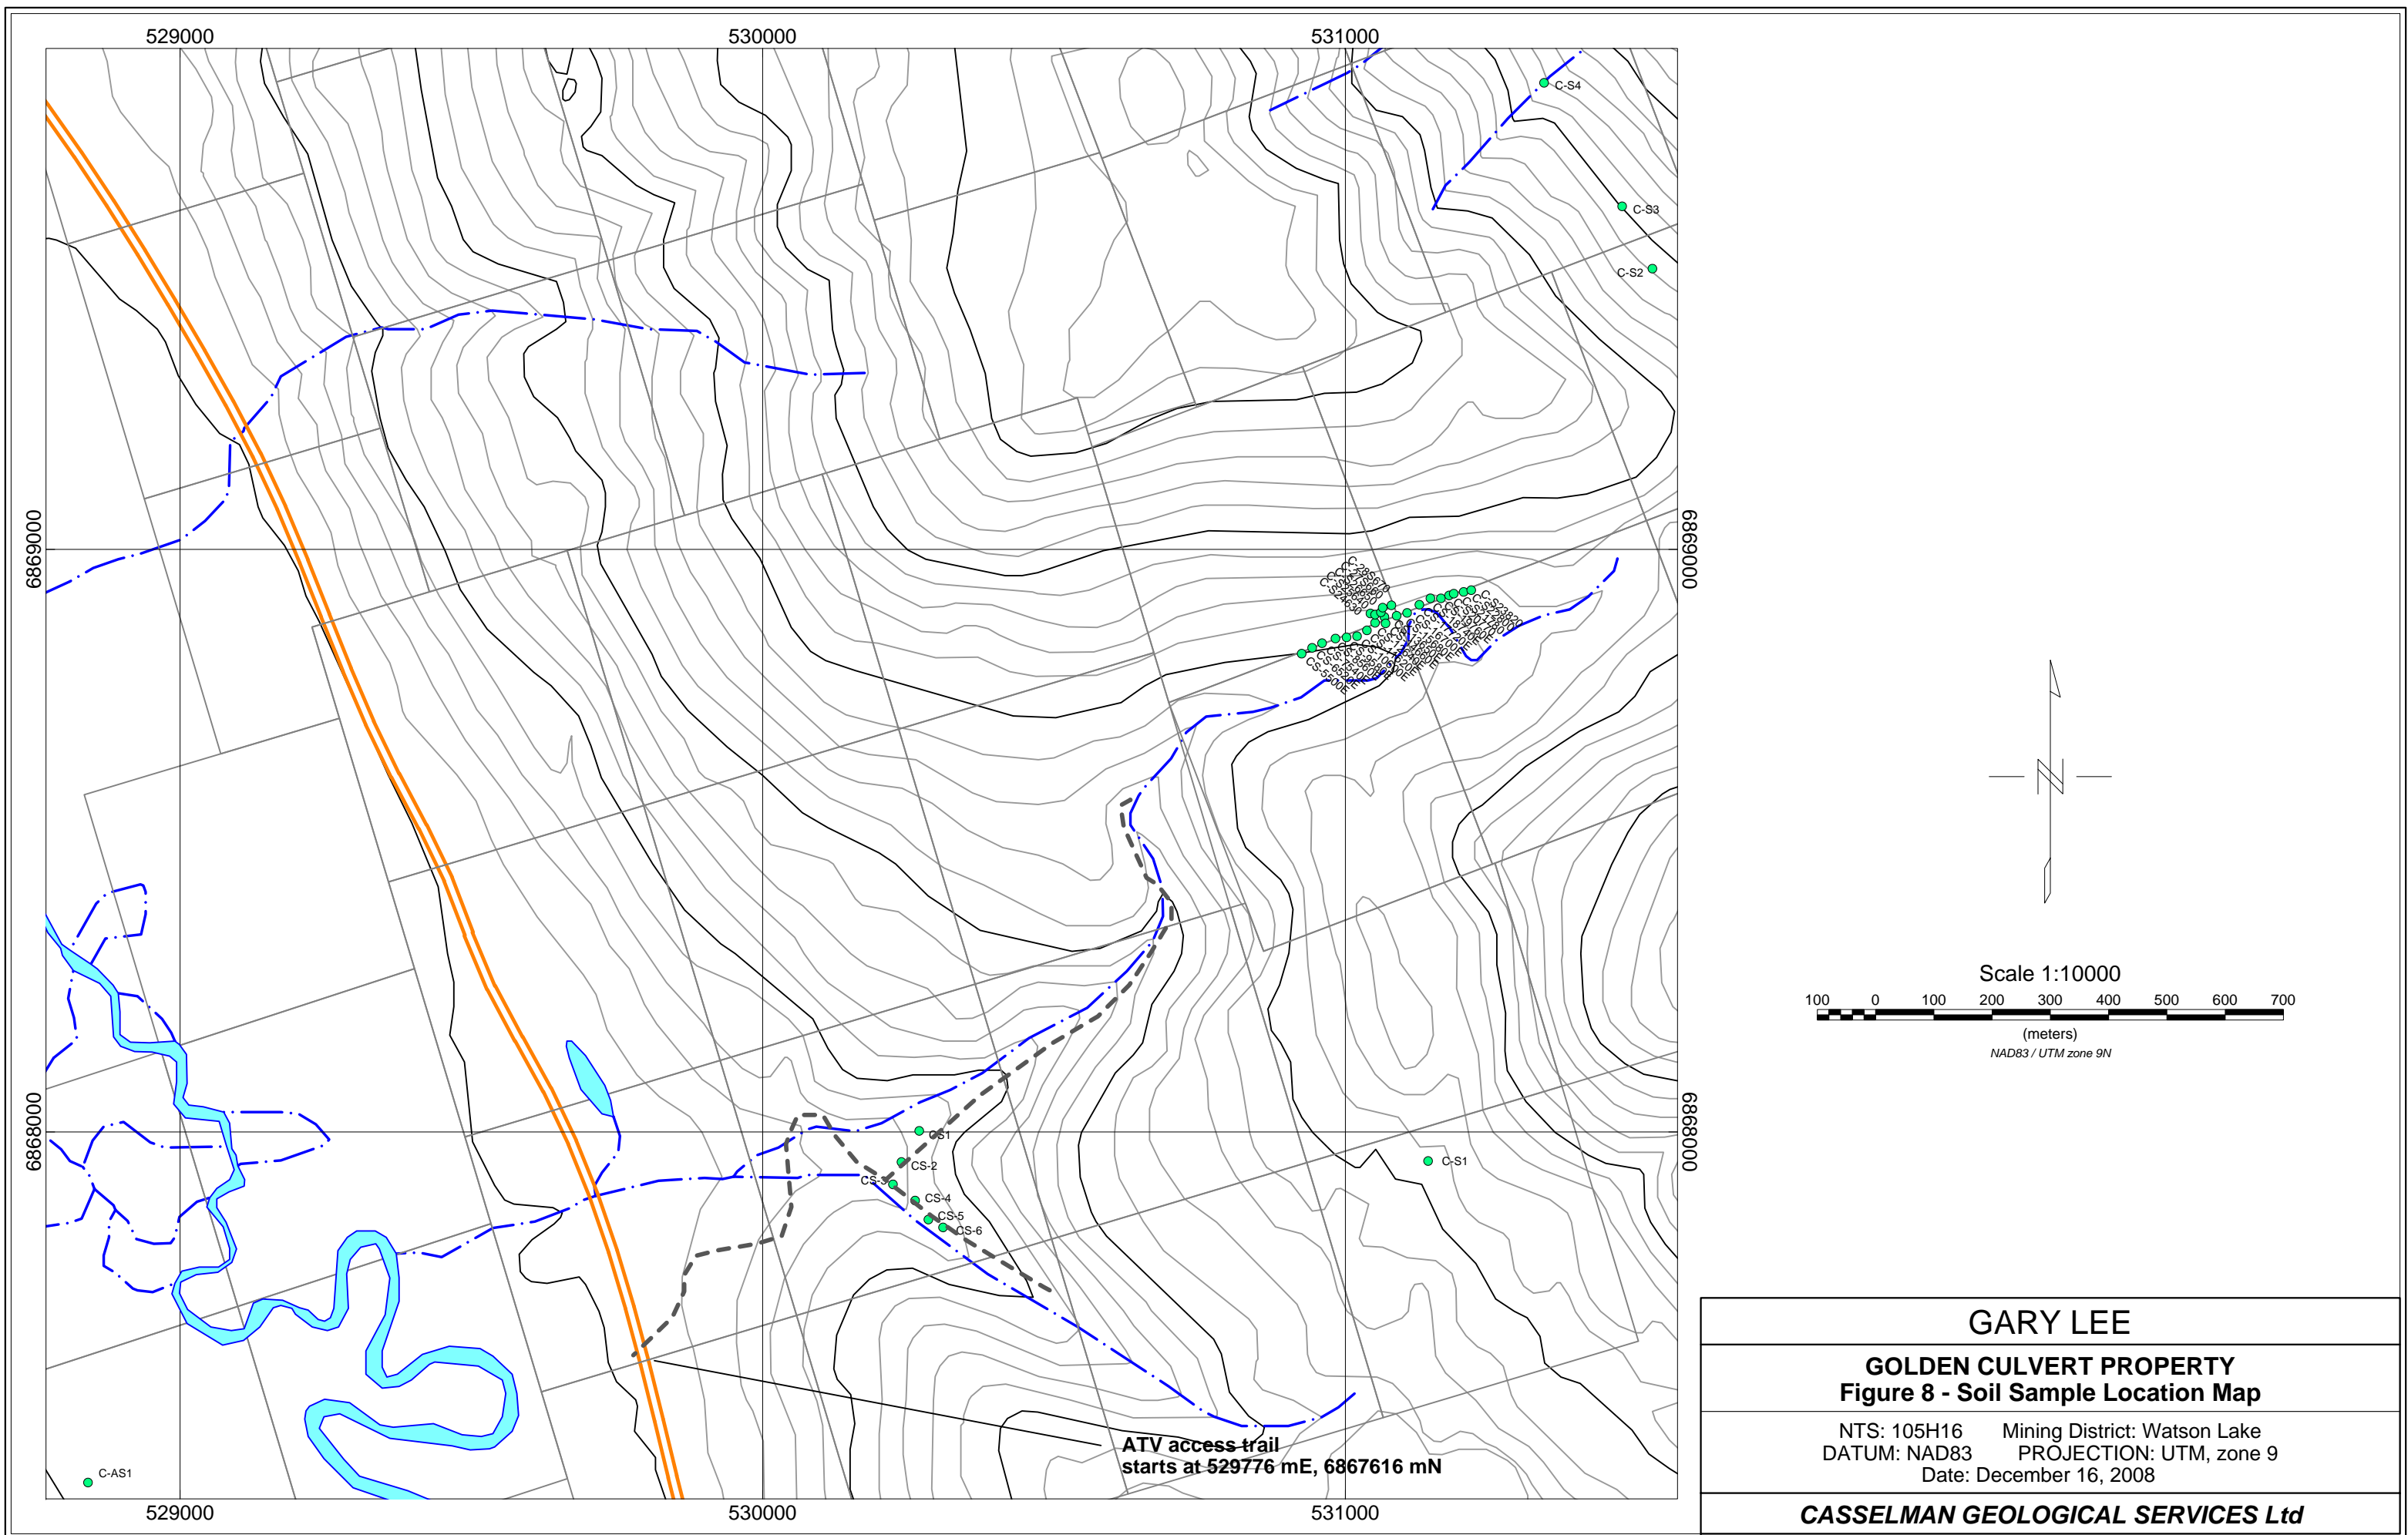

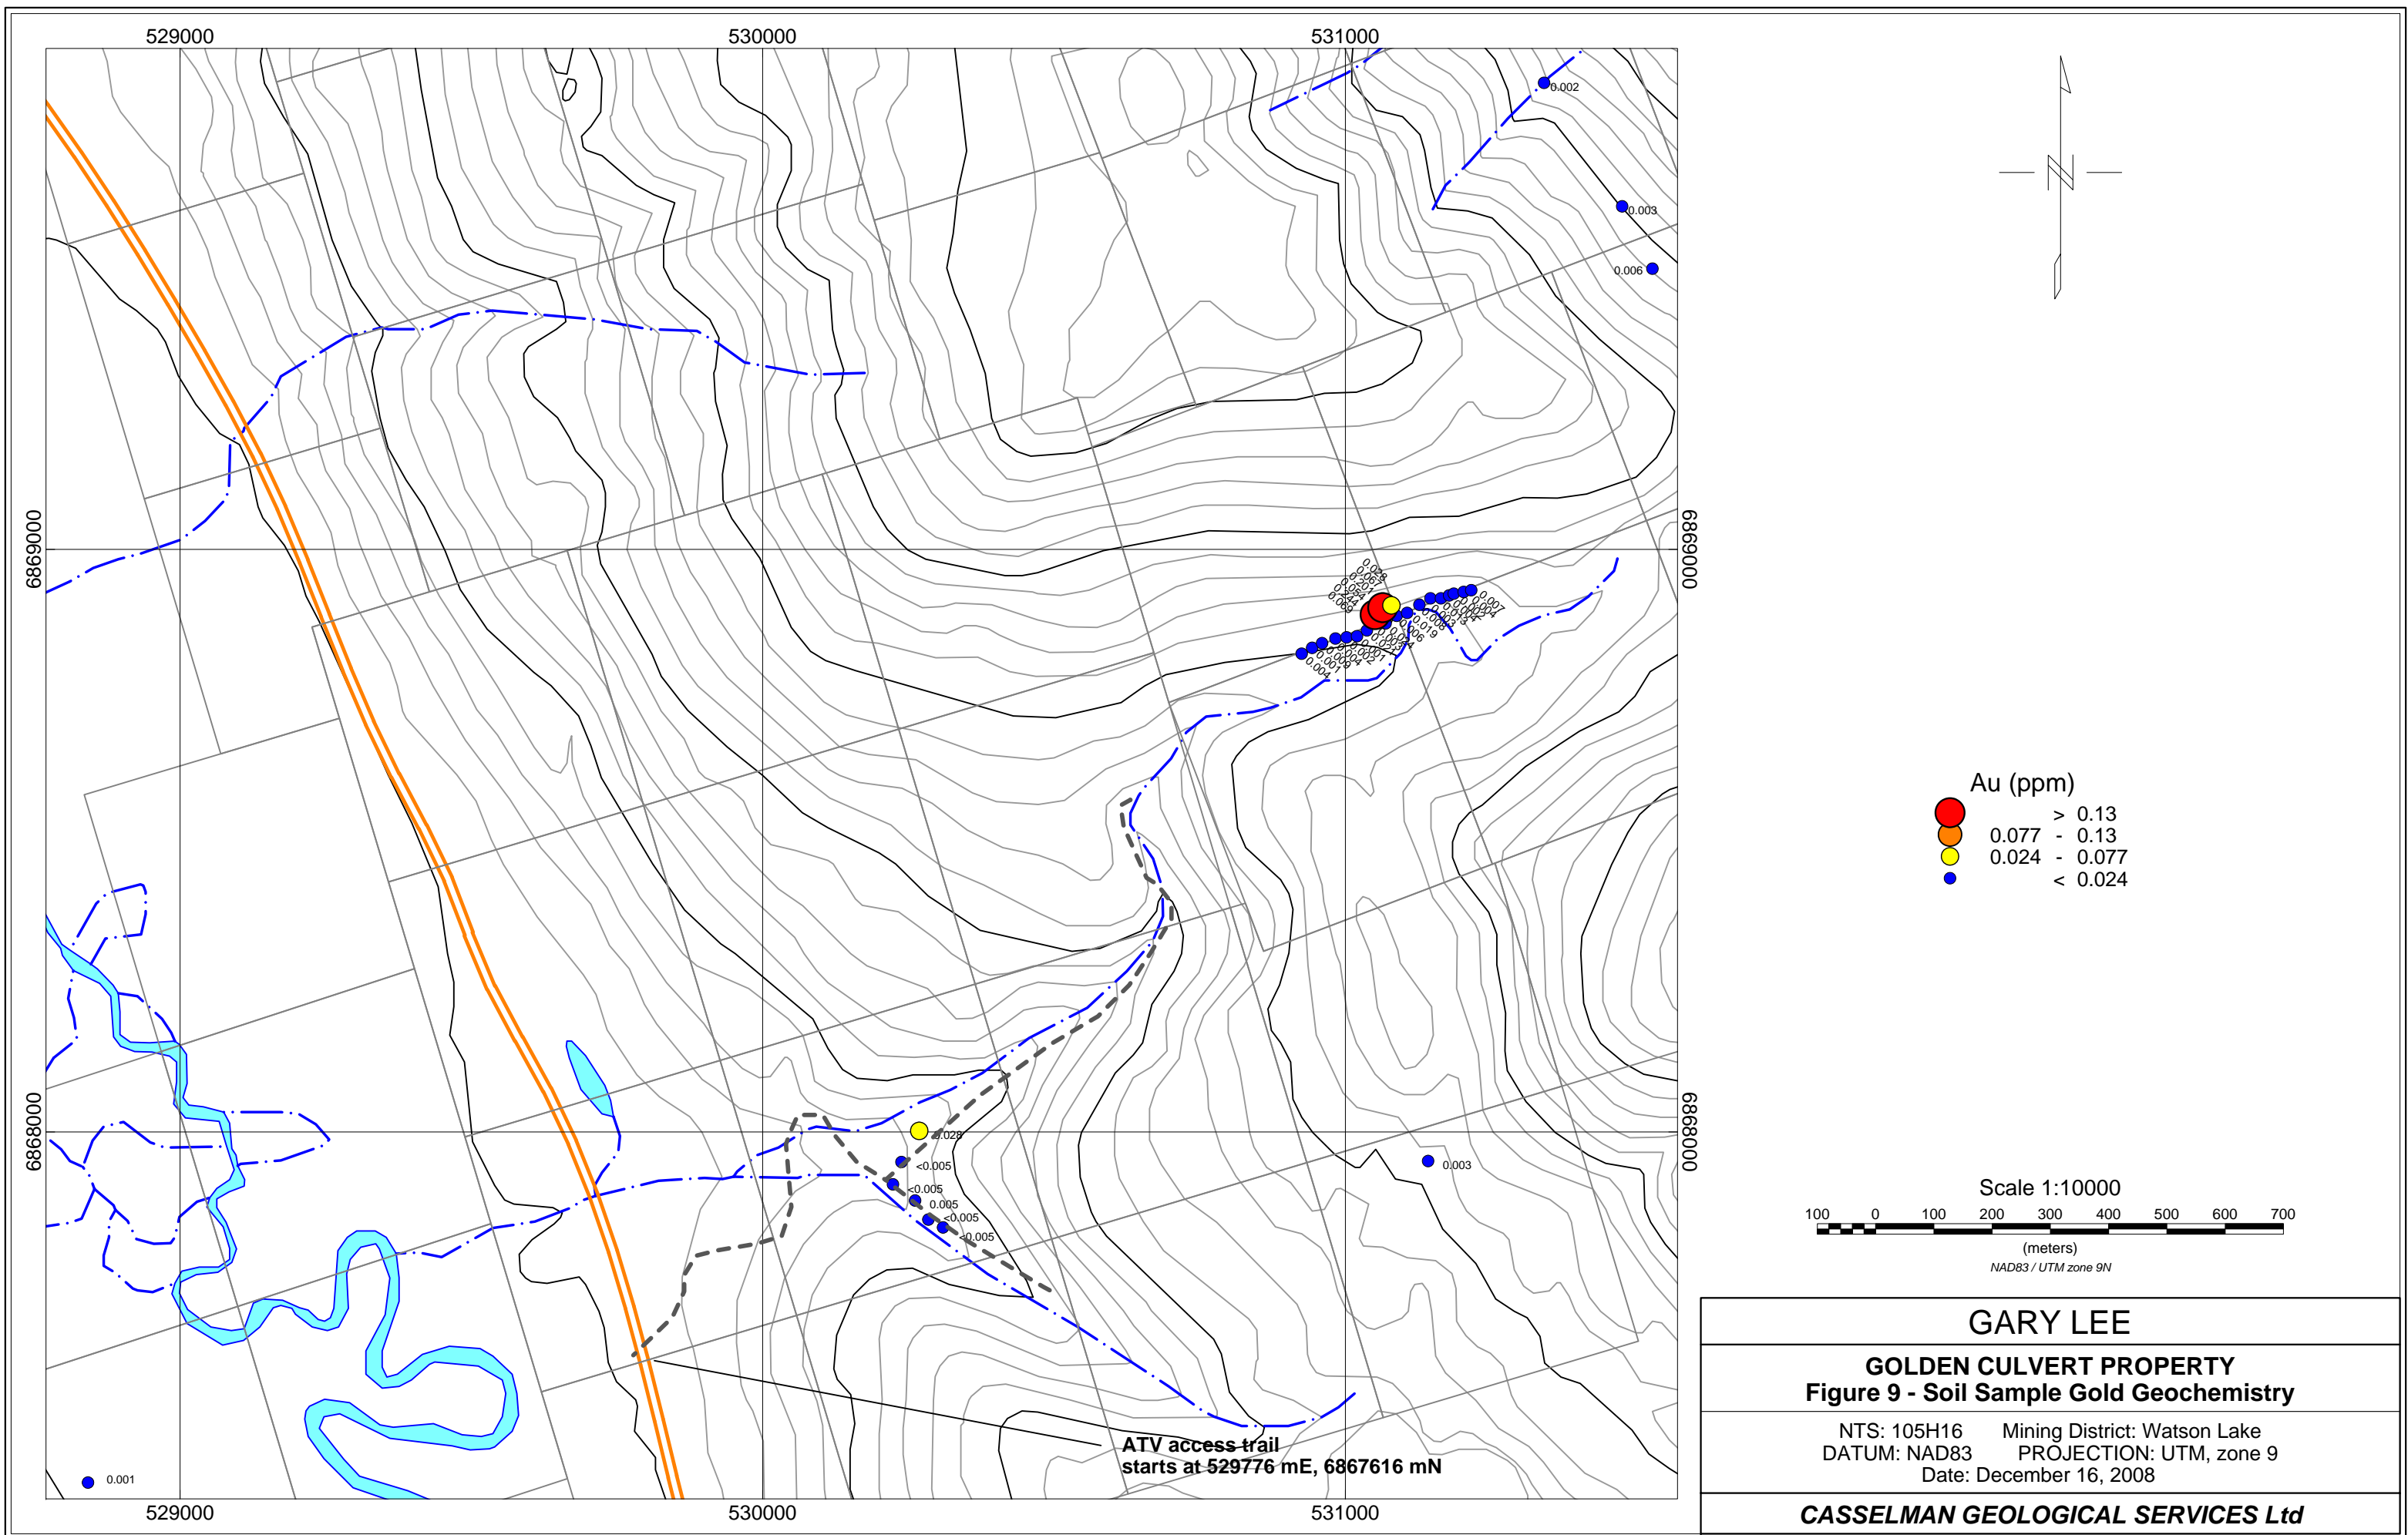


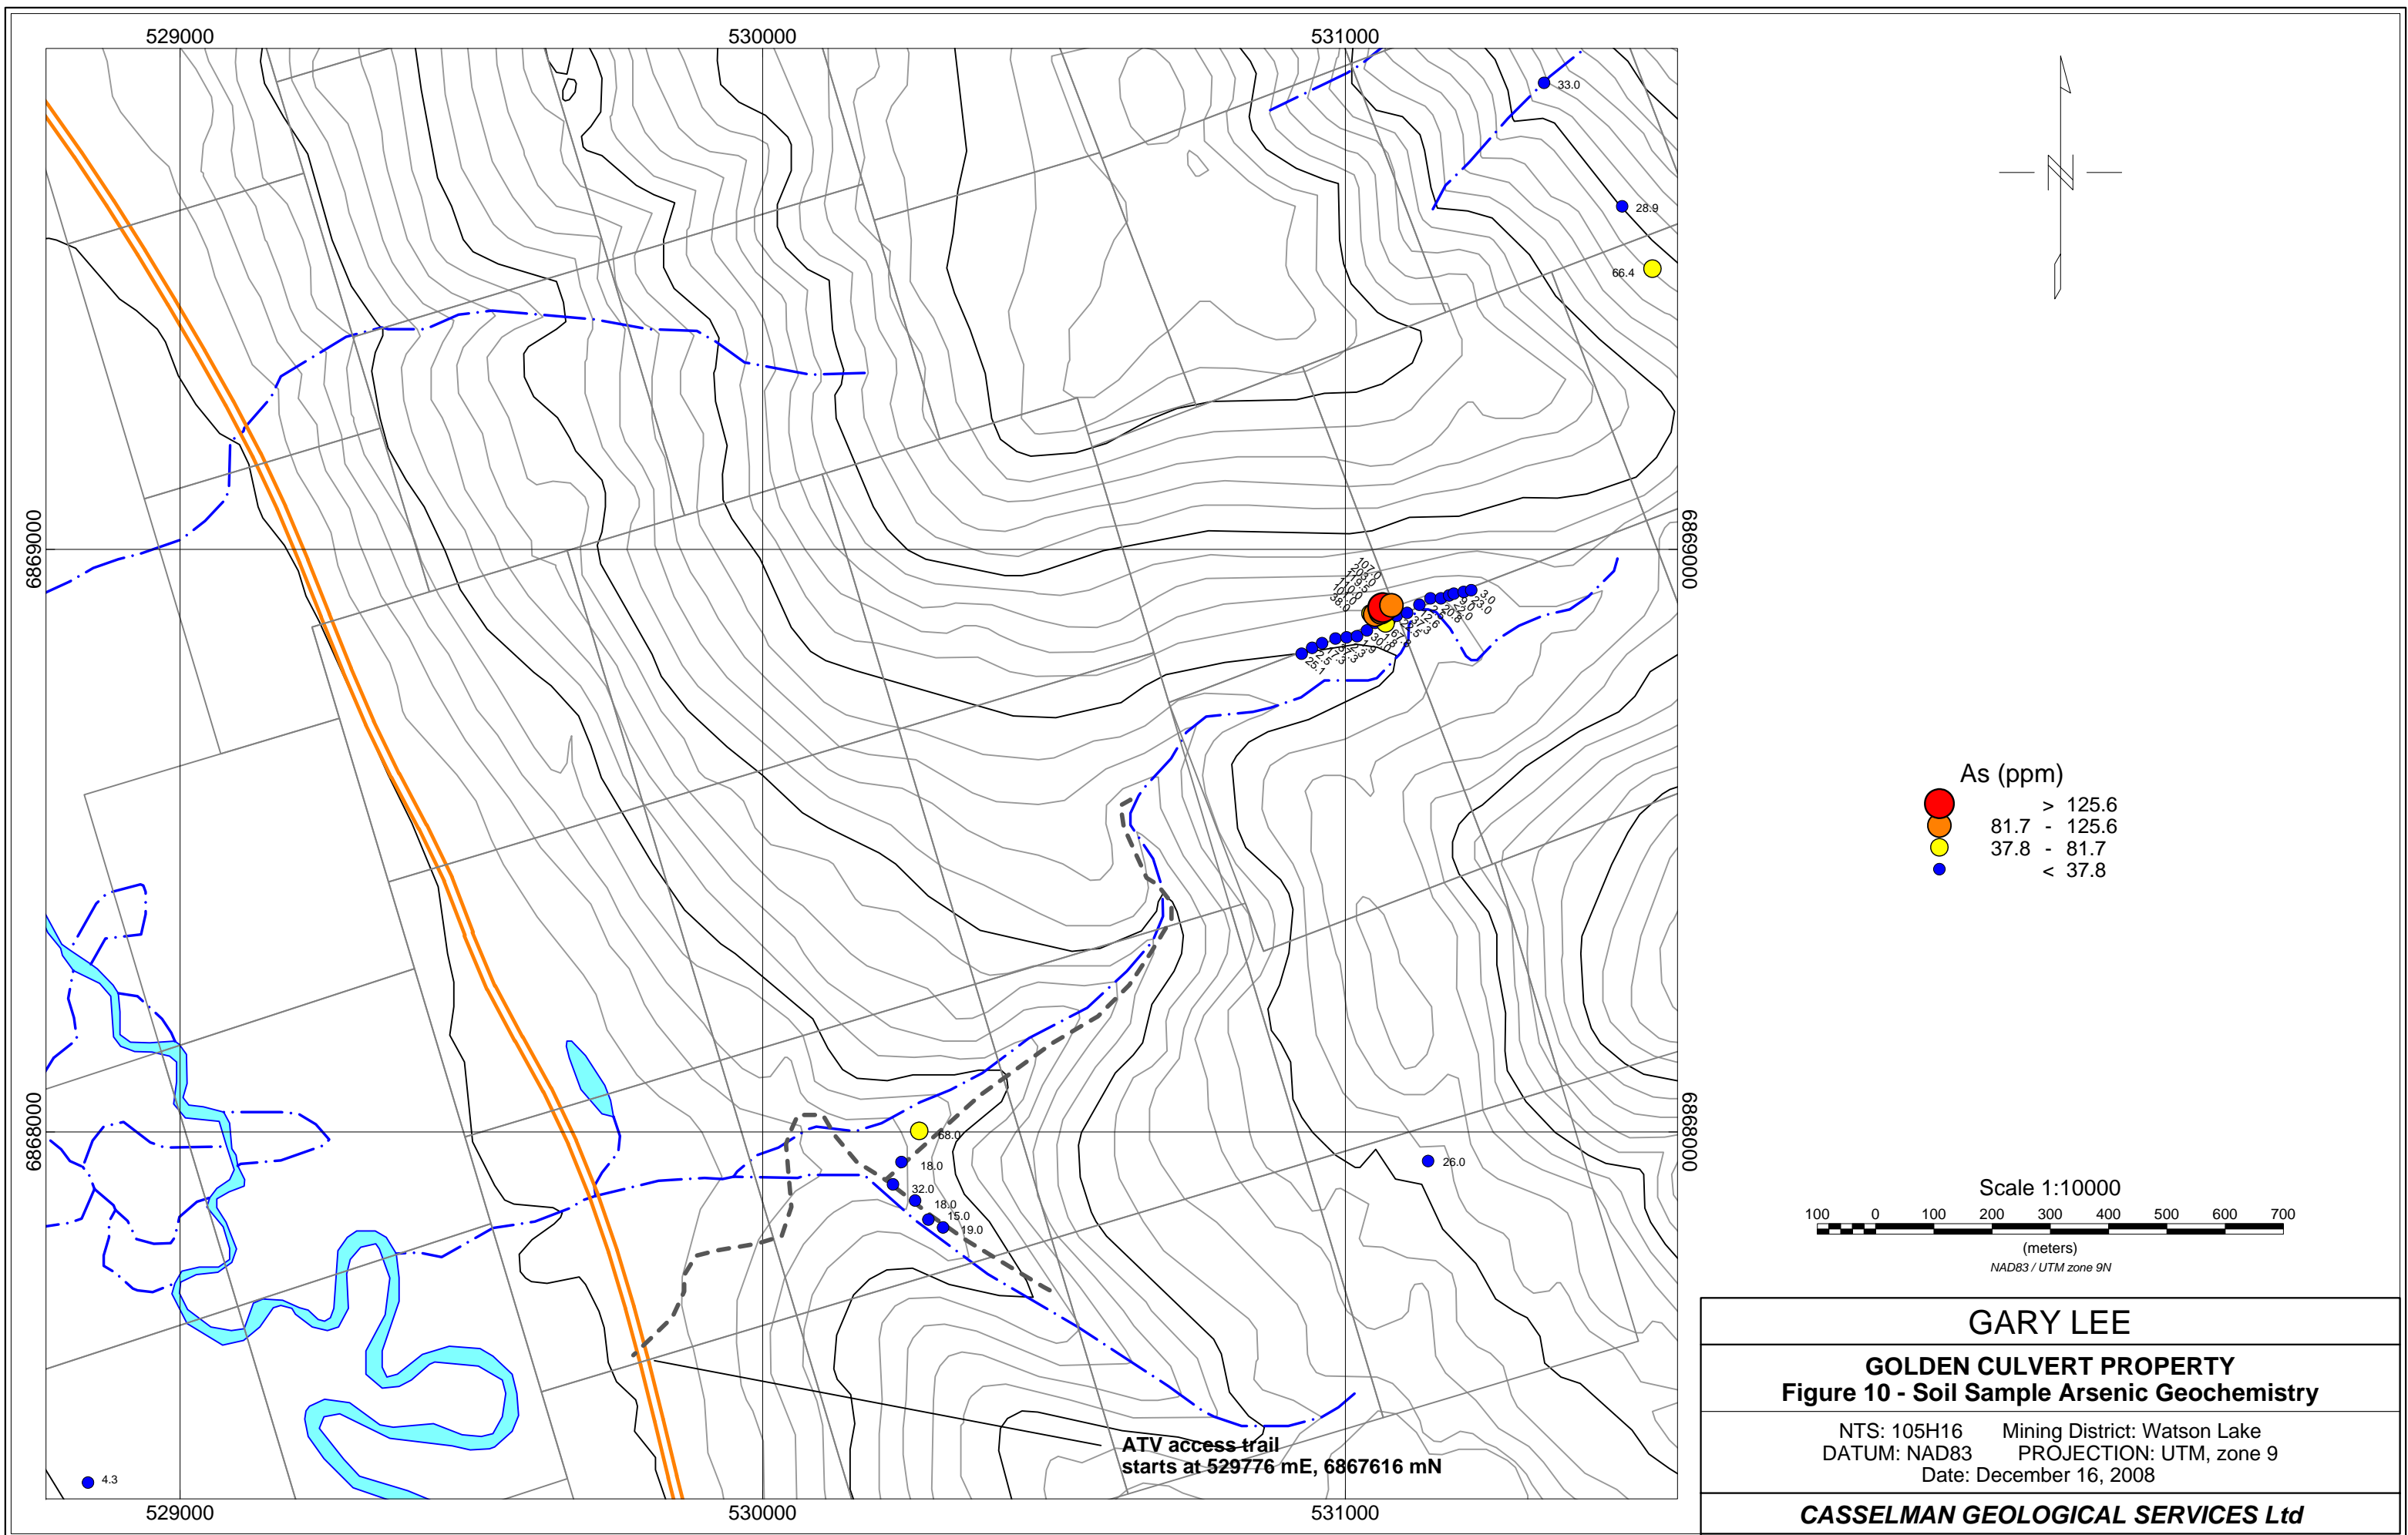


GARY LEE

GOLDEN CULVERT PROPERTY
Figure 10 - Soil Sample Arsenic Geochemistry

NTS: 105H16 Mining District: Watson Lake
 DATUM: NAD83 PROJECTION: UTM, zone 9
 Date: December 16, 2008

CASSELMAN GEOLOGICAL SERVICES Ltd

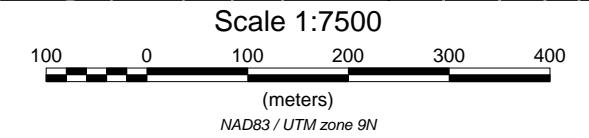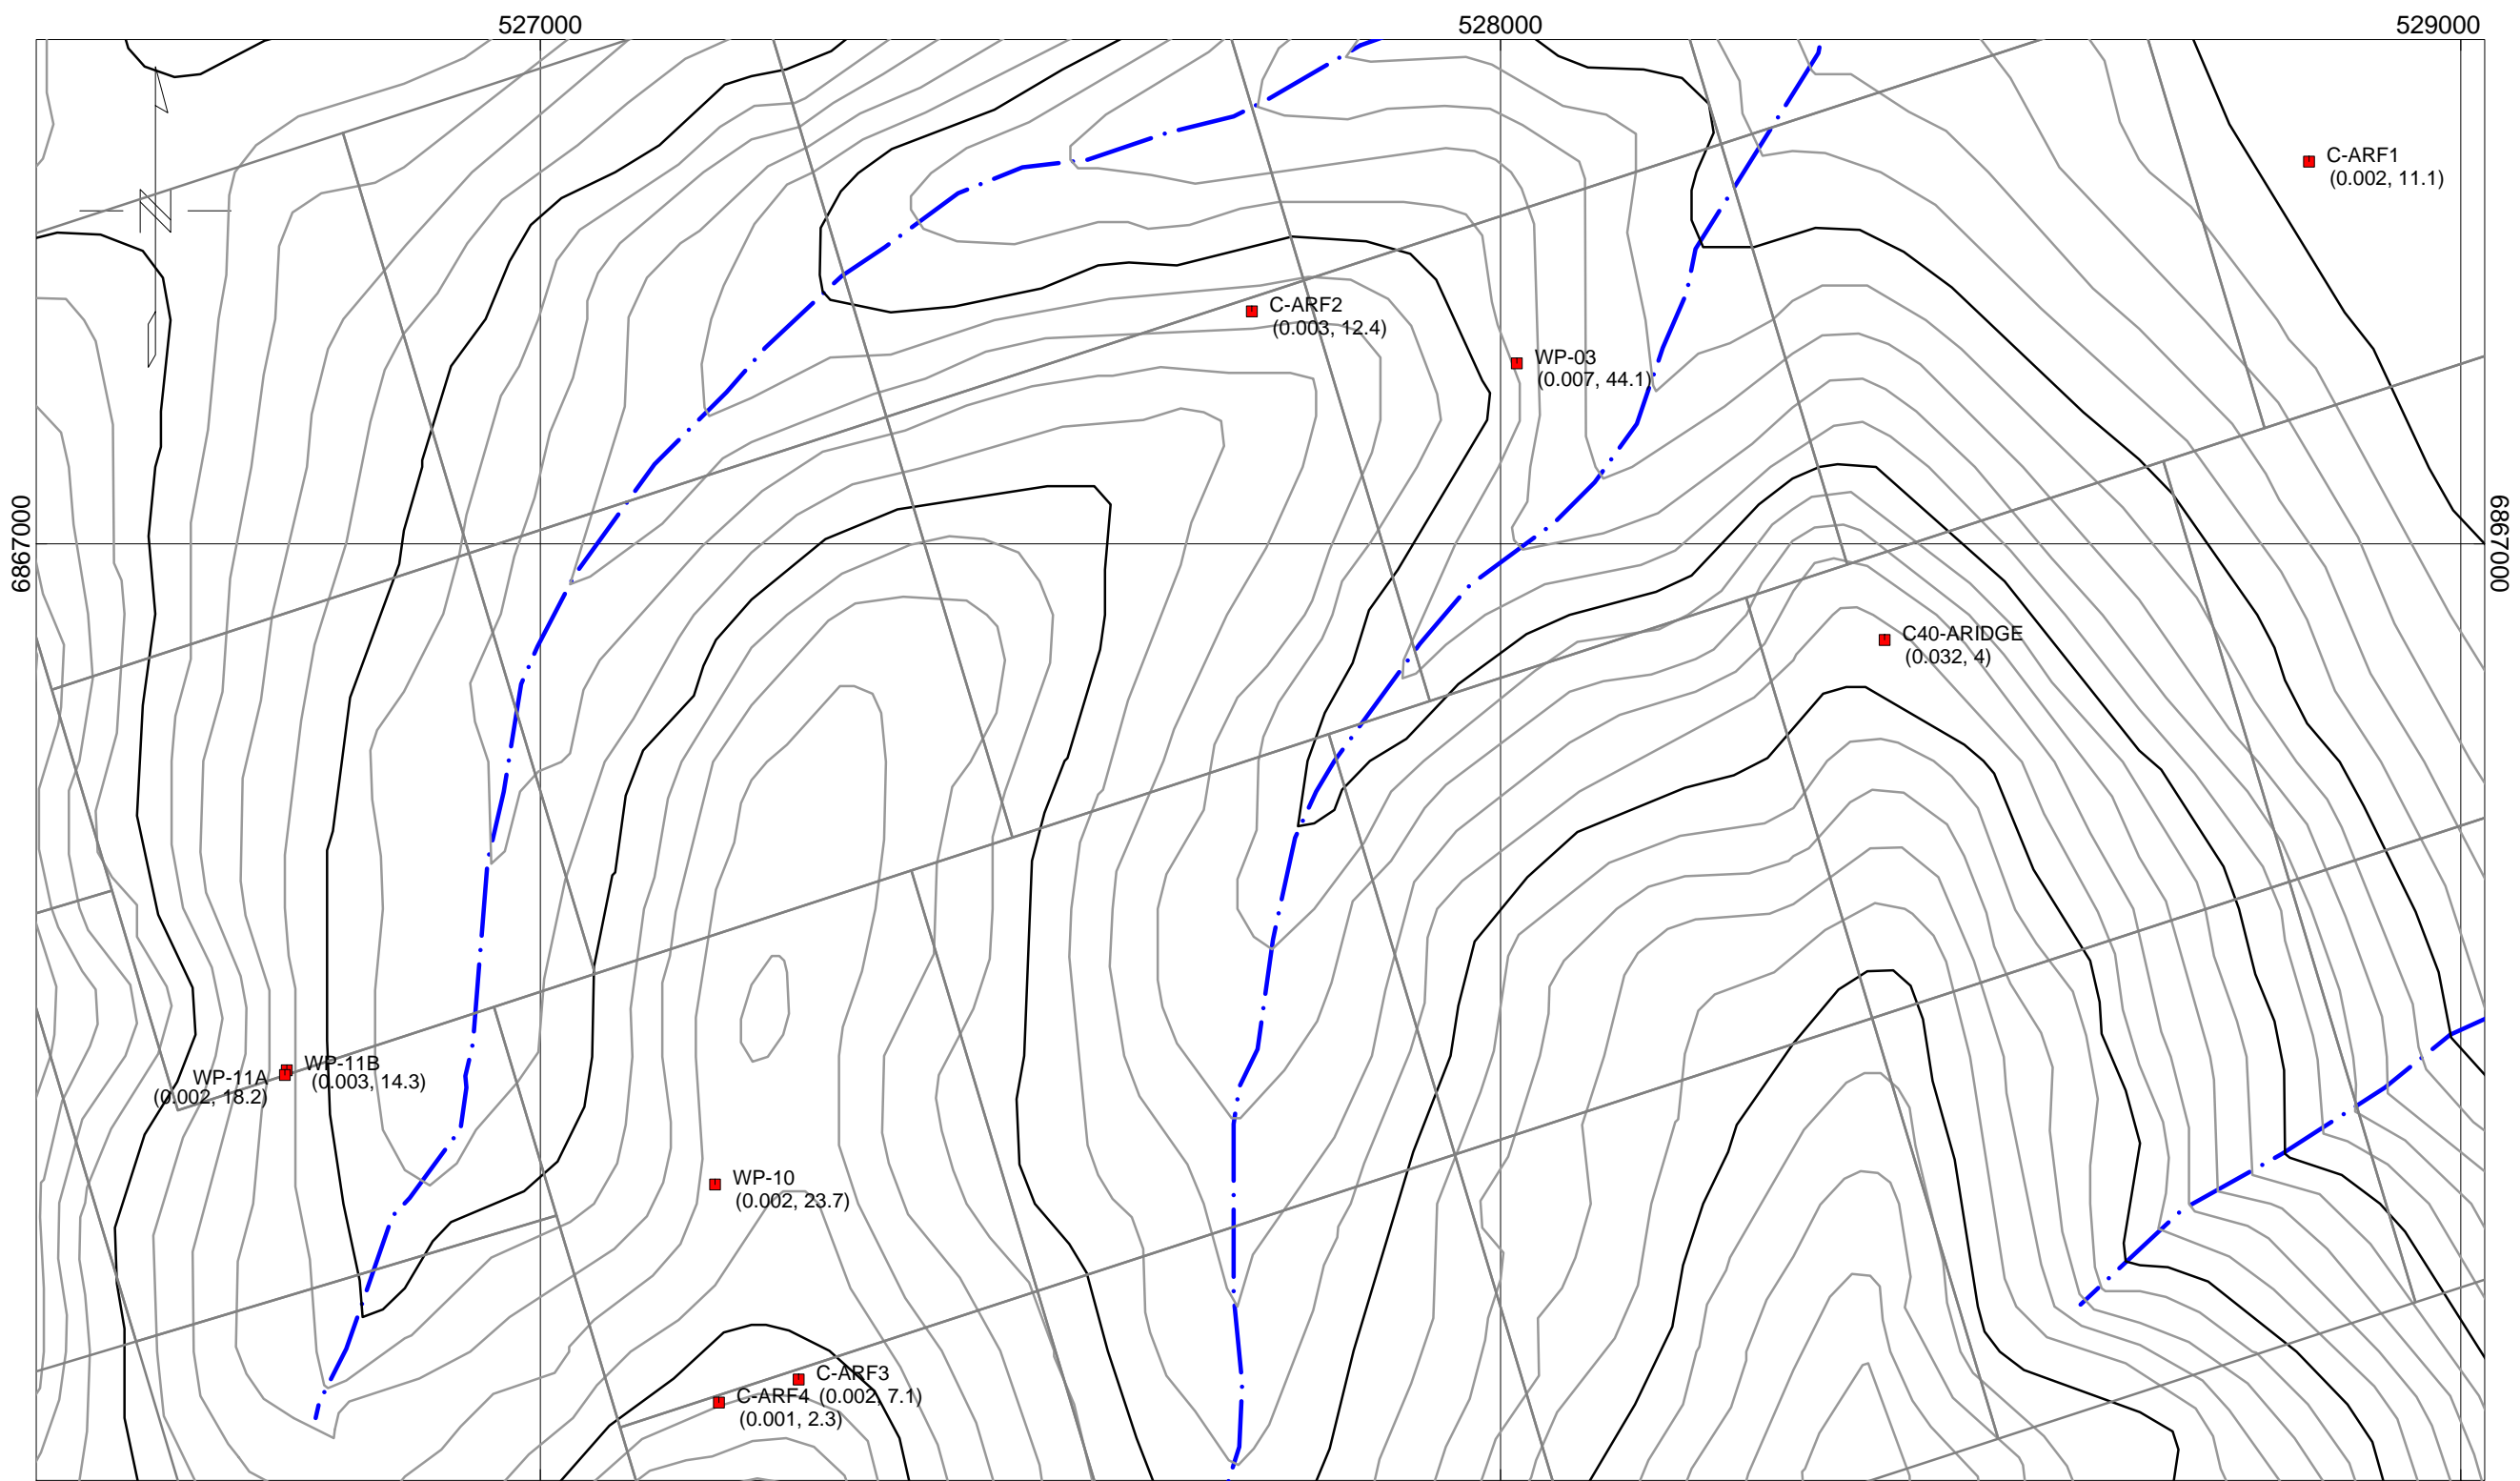


C-ARF 2 (0.002, 34.2) ■ Rock sample location sample number (Au ppm, As ppm)

OC Outcrop

RF Rock Float



| | |
|--|------------------------------|
| GARY LEE | |
| GOLDEN CULVERT PROPERTY | |
| Figure 11 - Rock Sample Location Map (West Sheet) | |
| NTS: 105H16 | Mining District: Watson Lake |
| DATUM: NAD83 | PROJECTION: UTM, zone 9 |
| Date: December 16, 2008 | |
| CASSELMAN GEOLOGICAL SERVICES Ltd | |

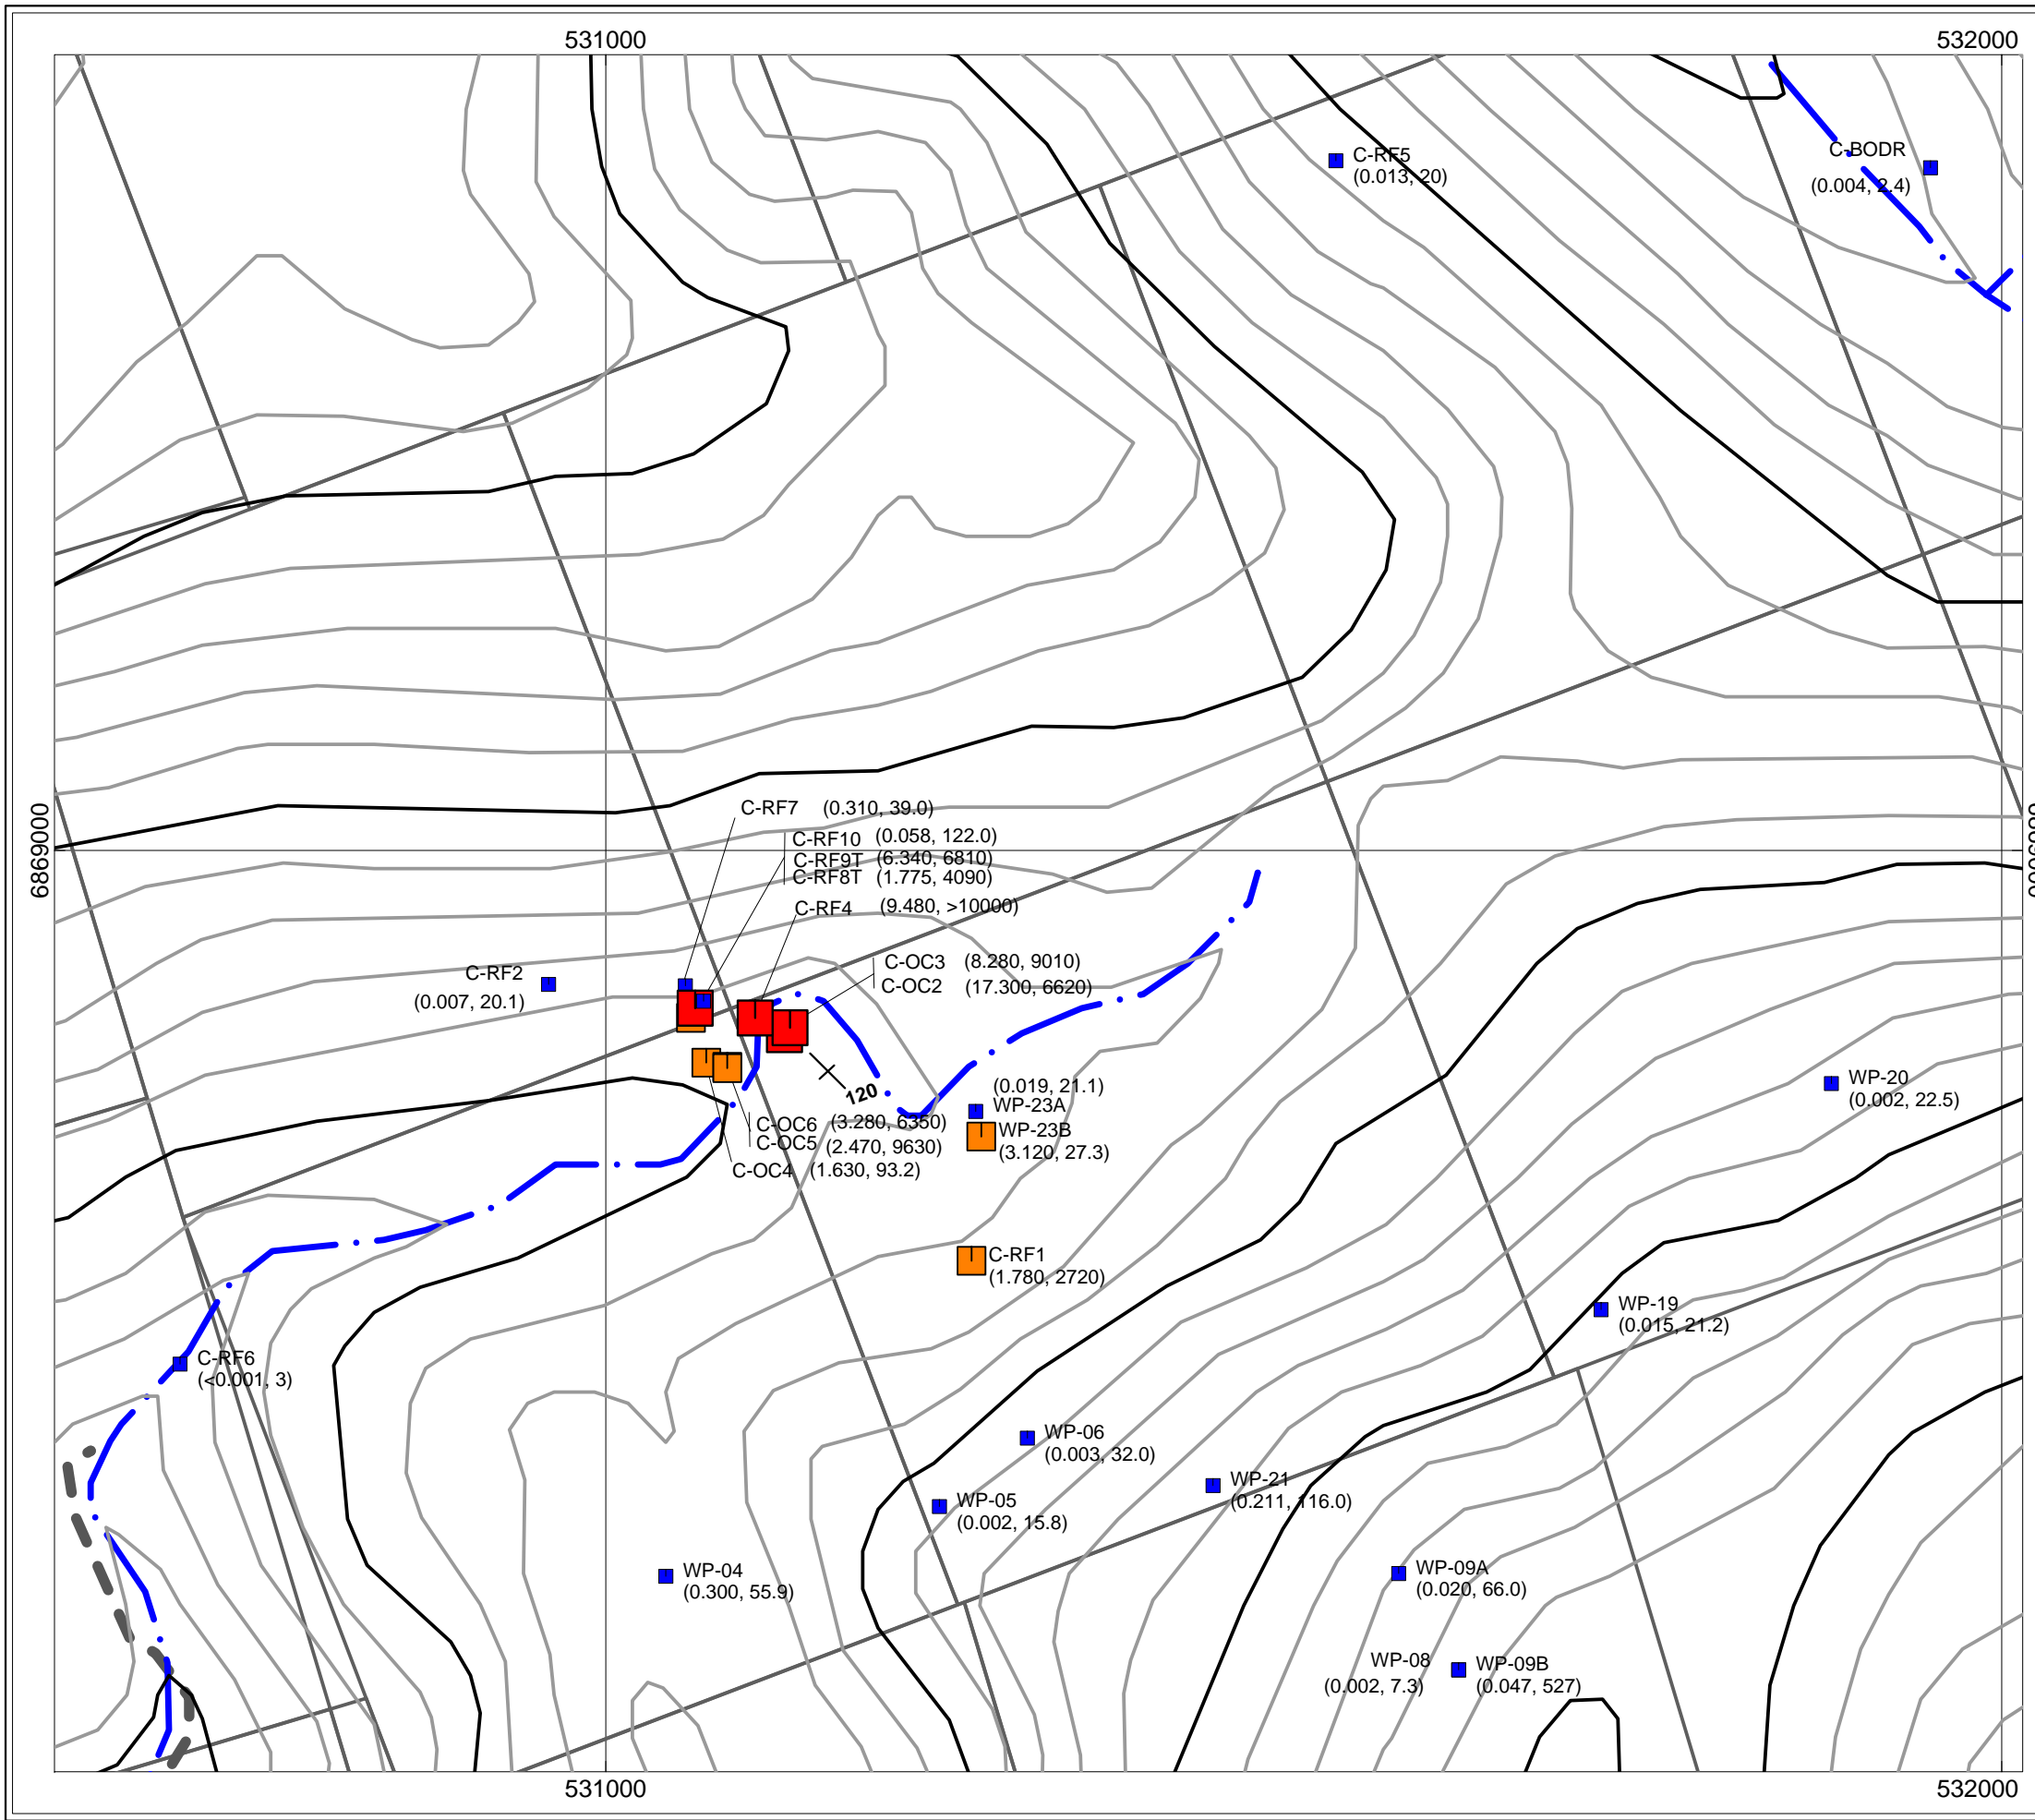


C-ARF 2 (0.002, 34.2) ■ Rock sample location ■ sample number (Au ppm, As ppm)

OC Outcrop

RF Rock Float

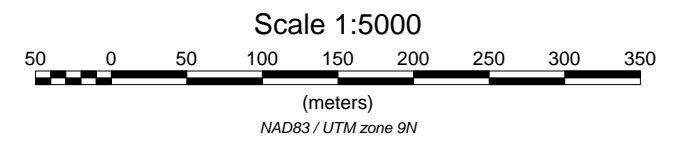

| | |
|--|------------------------------|
| GARY LEE | |
| GOLDEN CULVERT PROPERTY | |
| Figure 12 - Rock Sample Location Map (East Sheet) | |
| NTS: 105H16 | Mining District: Watson Lake |
| DATUM: NAD83 | PROJECTION: UTM, zone 9 |
| Date: December 16, 2008 | |
| CASSELMAN GEOLOGICAL SERVICES Ltd | |


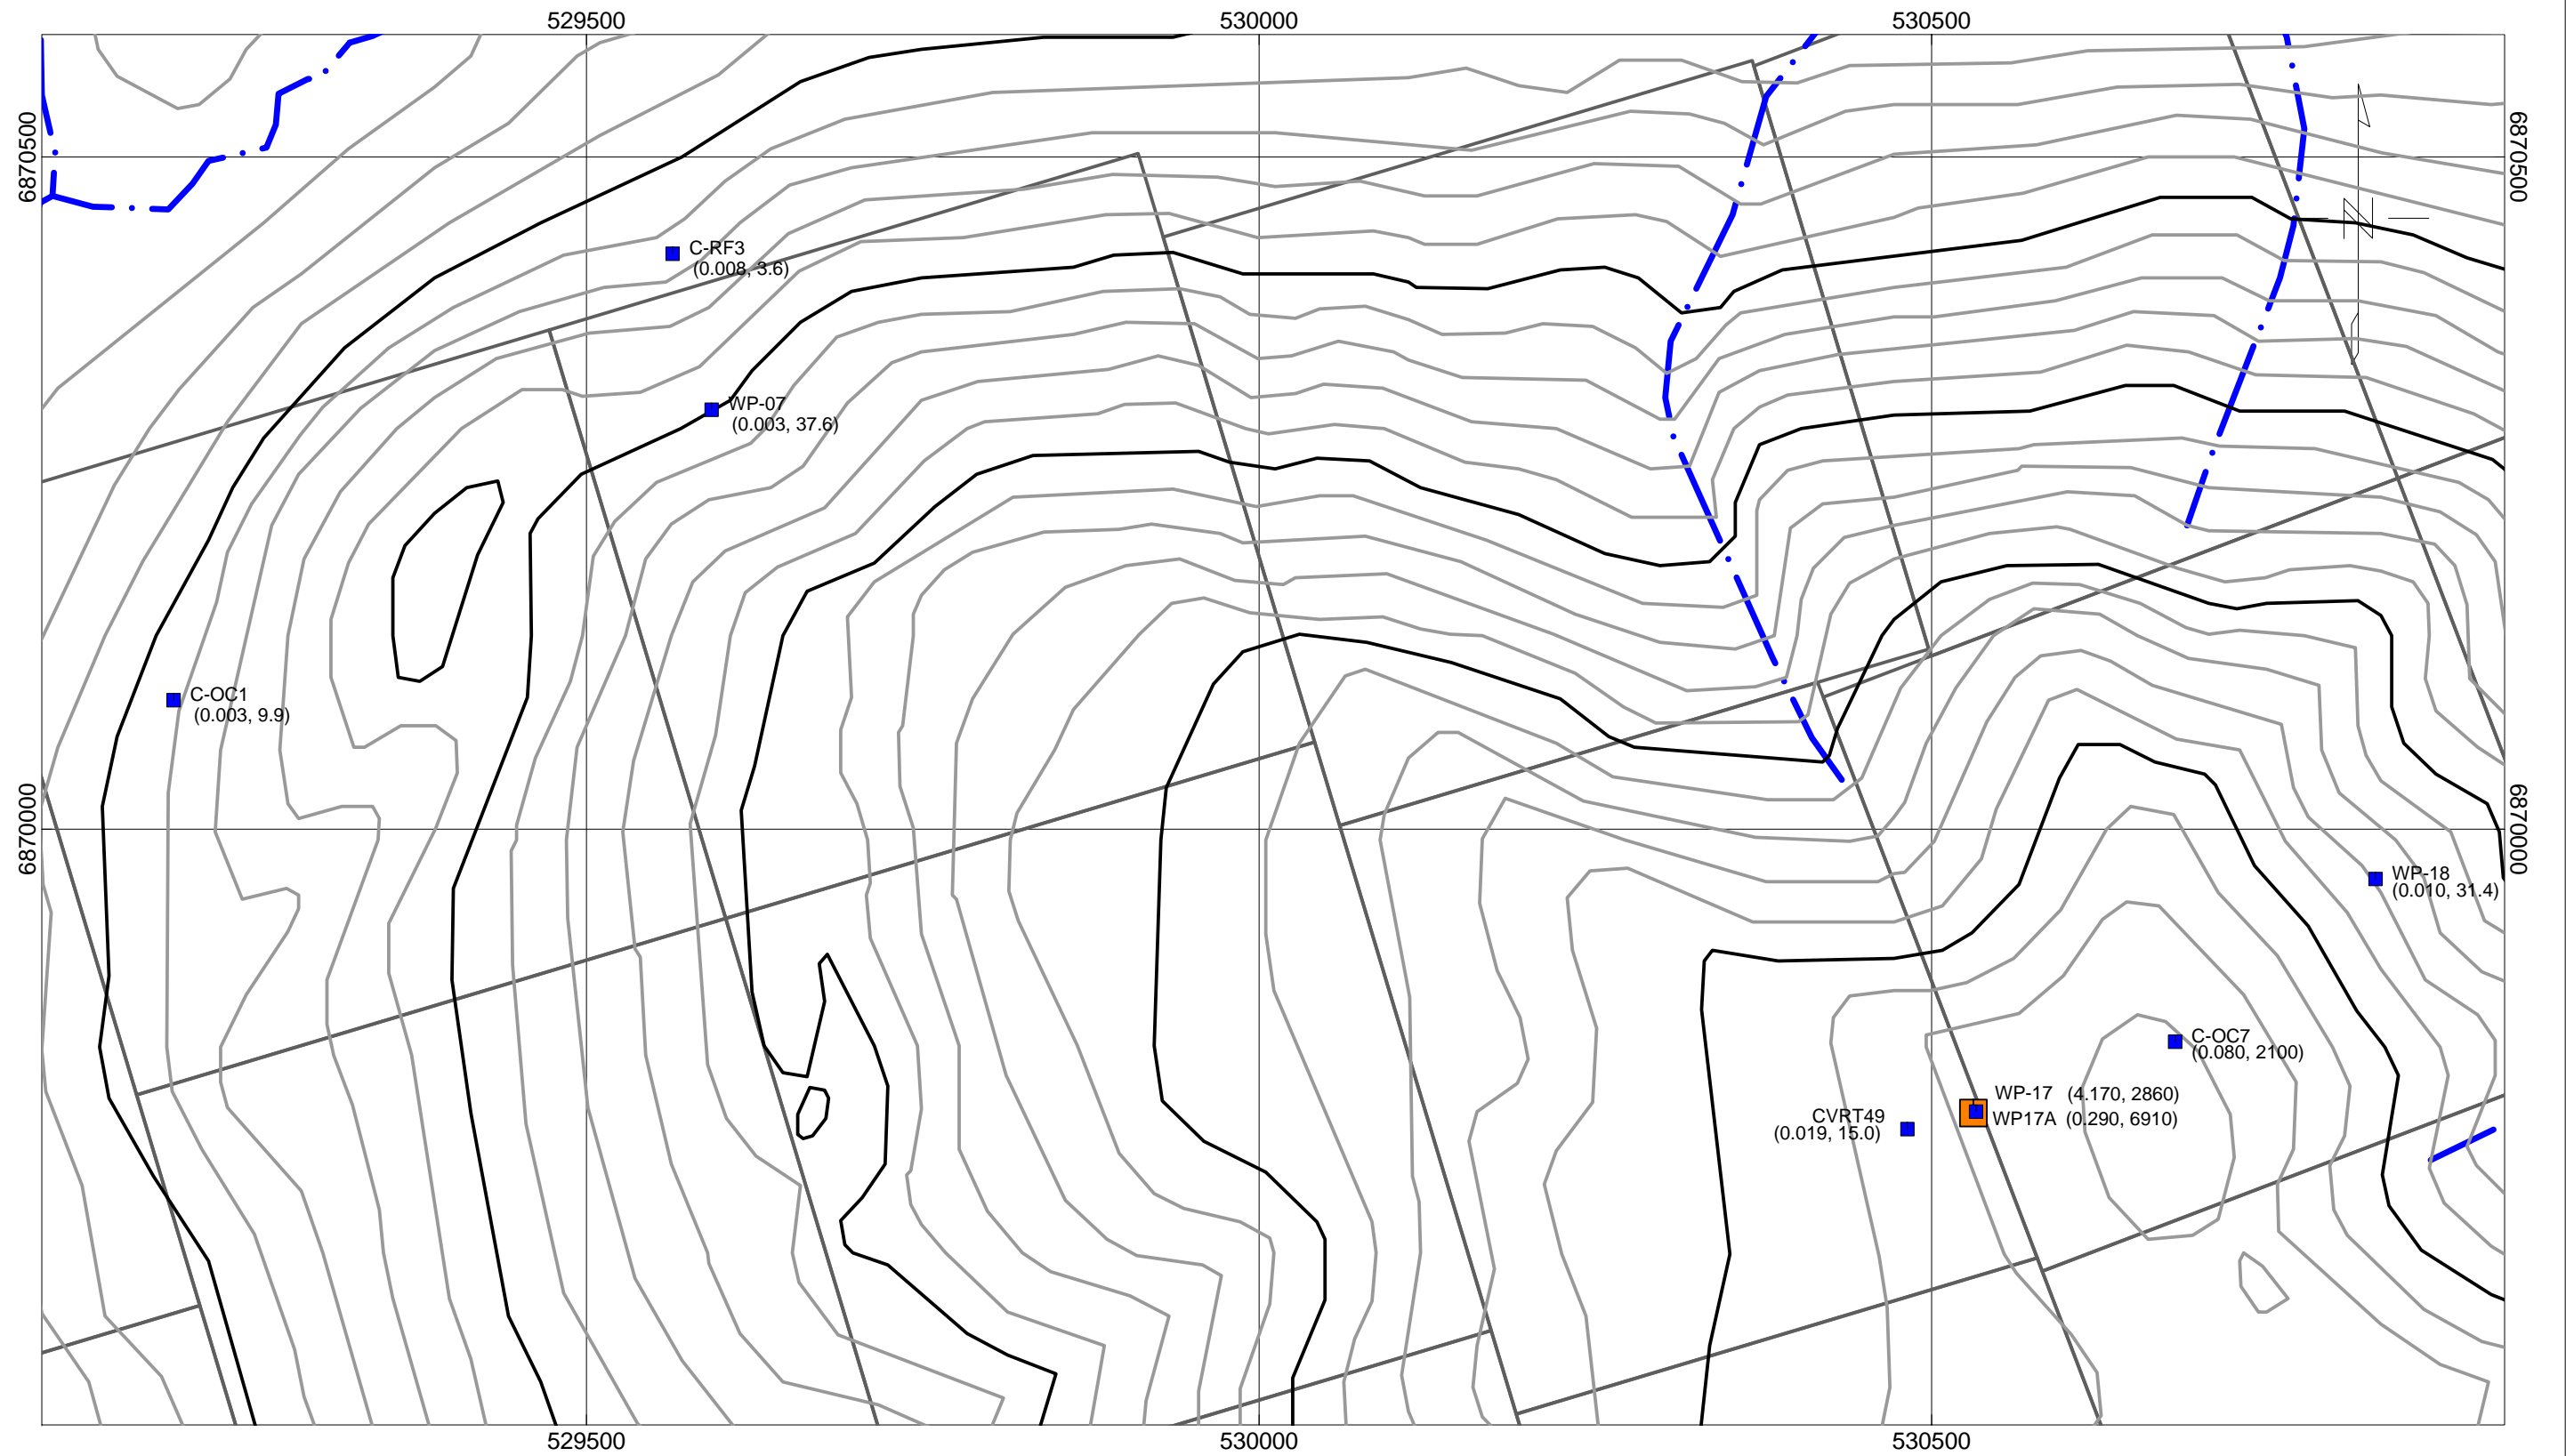


C-ARF 2
(0.002, 34.2)


OC Outcrop

RF Rock Float

sample number
(Au ppm, As ppm)

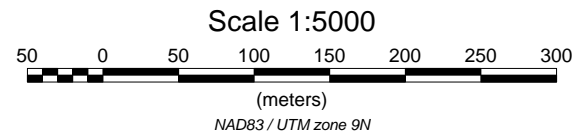

| | |
|---|------------------------------|
| GARY LEE | |
| GOLDEN CULVERT PROPERTY | |
| Figure 13 - Rock Sample Location Map (North Sheet) | |
| NTS: 105H16 | Mining District: Watson Lake |
| DATUM: NAD83 | PROJECTION: UTM, zone 9 |
| Date: December 16, 2008 | |
| CASSELMAN GEOLOGICAL SERVICES Ltd | |

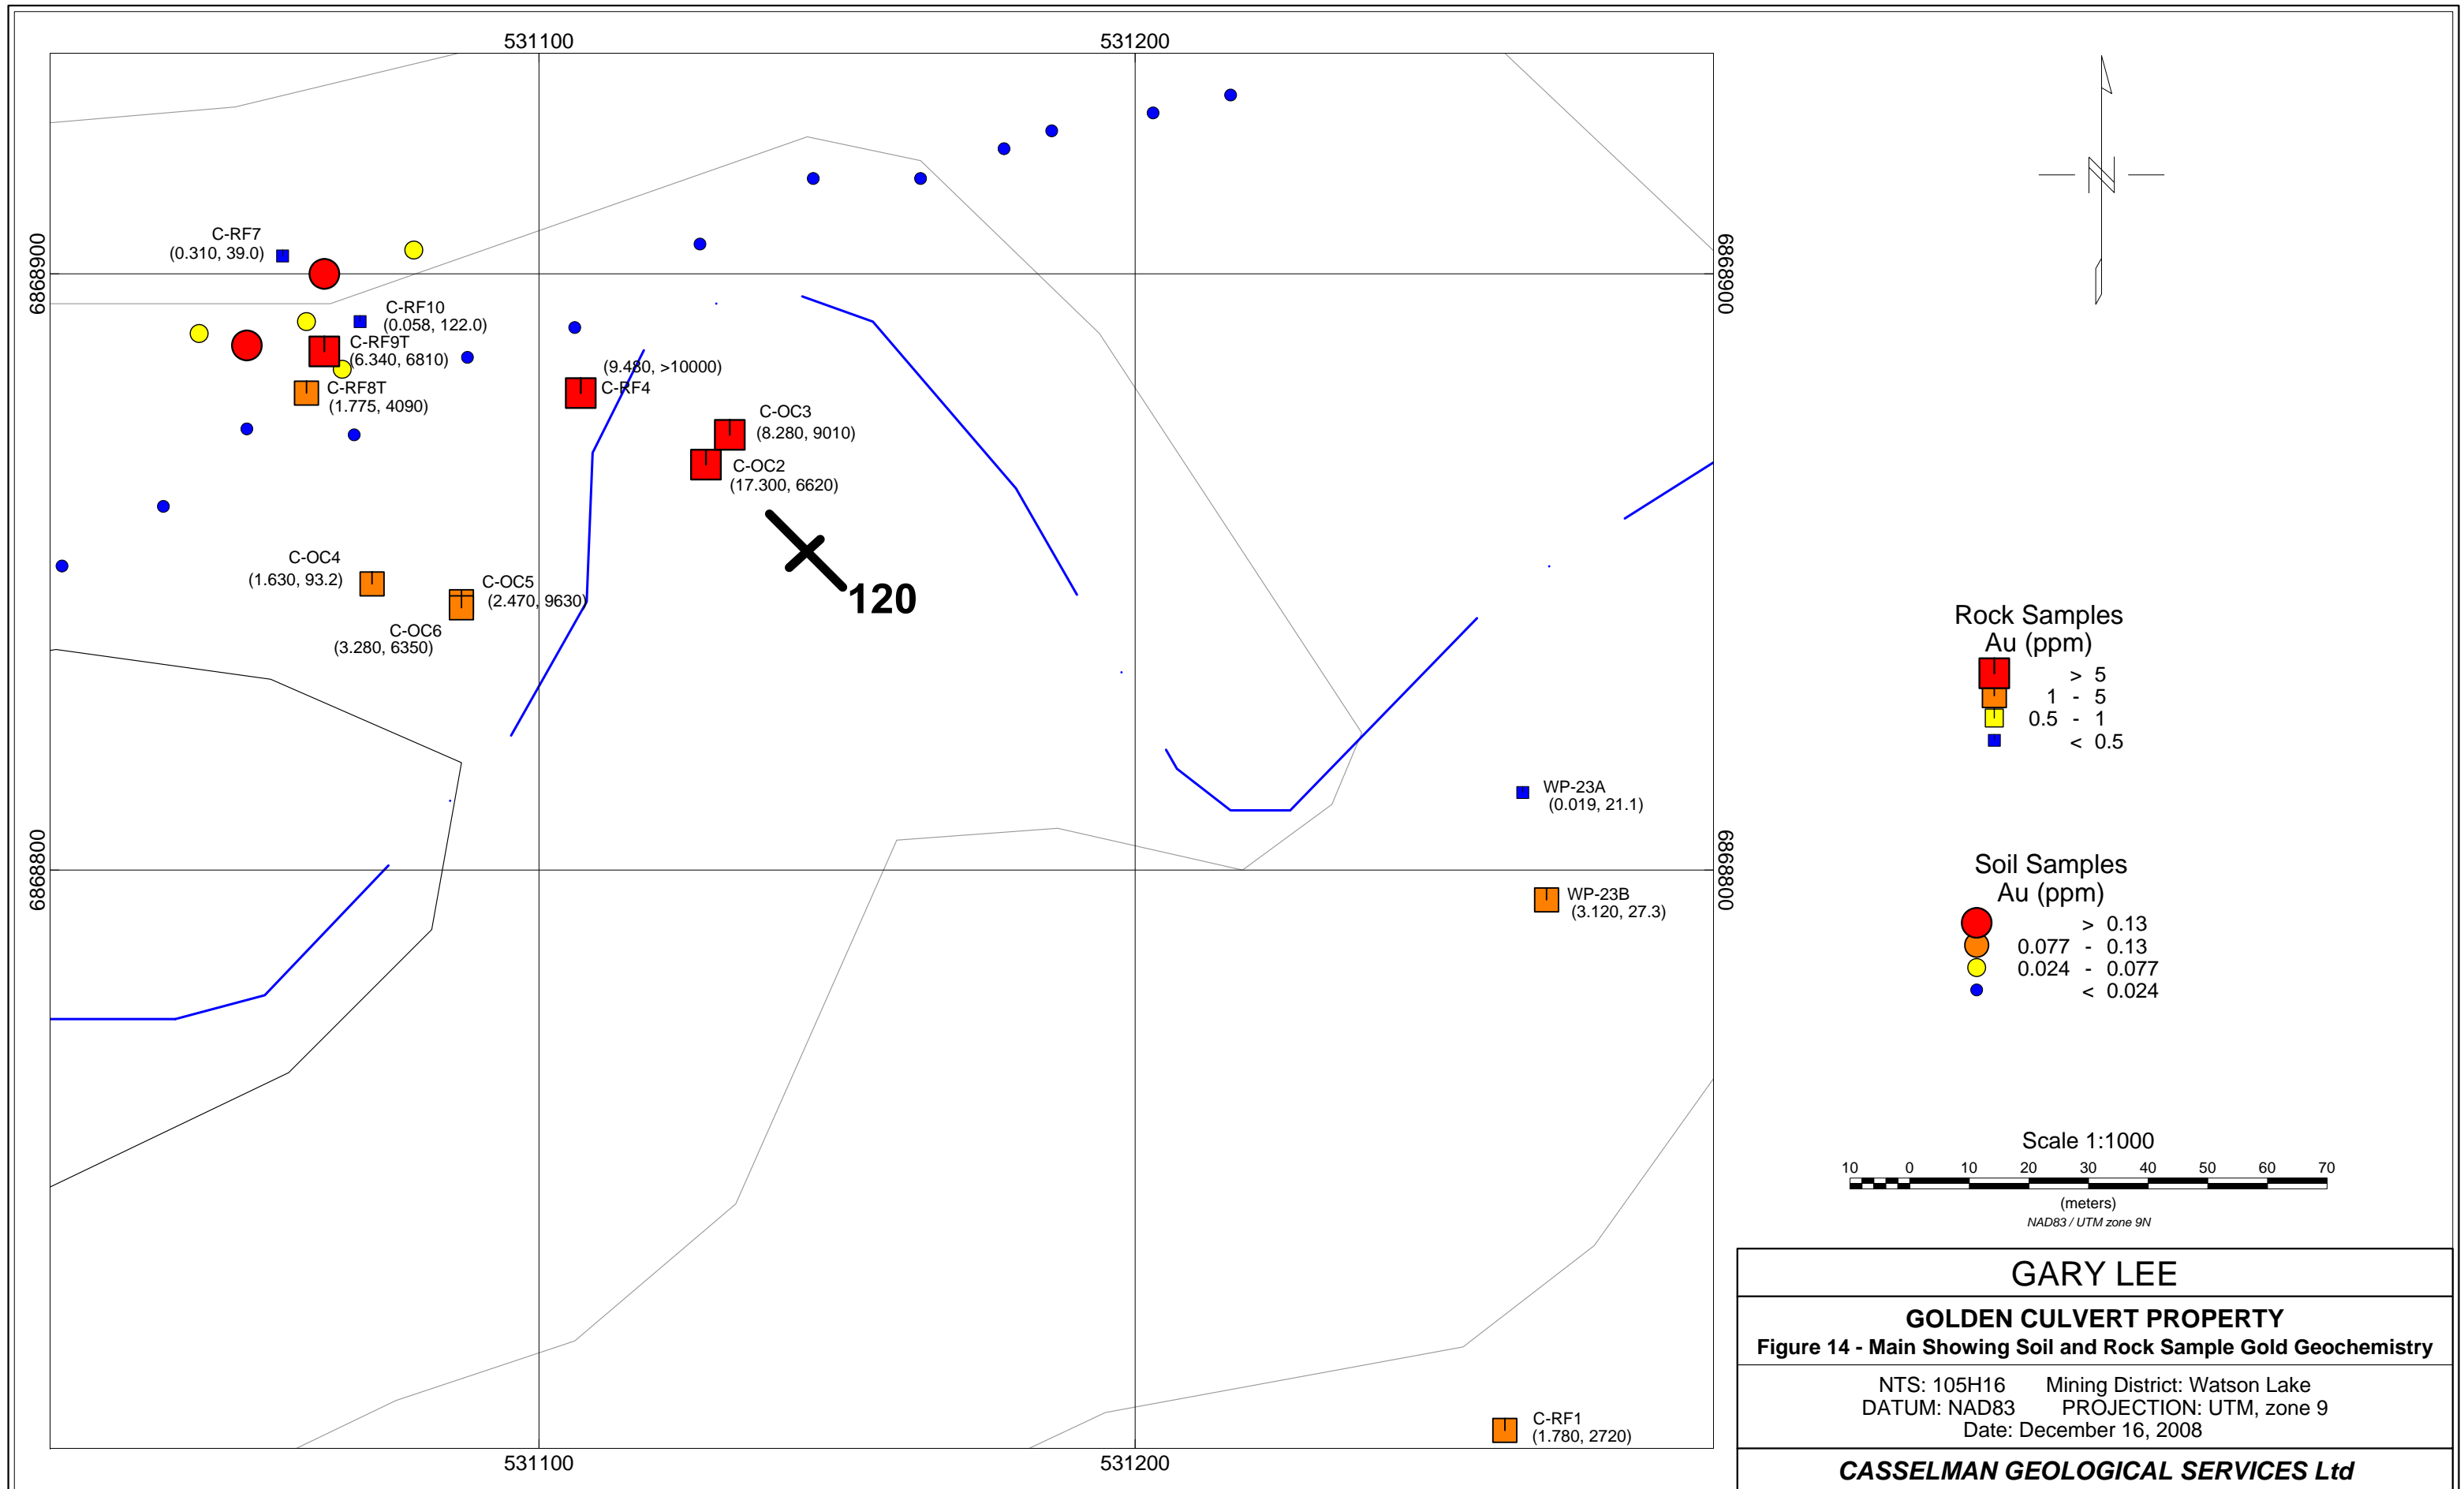

C-RF7
(0.310, 39.0)

C-RF10
(0.058, 122.0)

C-RF9T
(6.340, 6810)

C-RF8T
(1.775, 4090)

C-OC4
(1.630, 93.2)

C-OC6
(3.280, 6350)

C-OC5
(2.470, 9630)

(9.480, >10000)
C-RF4

C-OC3
(8.280, 9010)

C-OC2
(17.300, 6620)

X
120

WP-23A
(0.019, 21.1)

WP-23B
(3.120, 27.3)

C-RF1
(1.780, 2720)