



**SELWYN CHIHONG
MINING LTD.**

Suite 700 – 509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

Telephone: +1 (604) 801-7240
Toll-free: 1 (888)-989-7240

Fax: +1 (604) 689-8355
info@selwynresources.com
www.selwynresources.com

2010 Assessment Report

Describing
Prospecting, Geochemical Sampling and Diamond Drilling
on the

Selwyn Project

X, R, Don, OP, Anniv, D, DJ, and Knap claims
Under option to Selwyn Chihong Mining Ltd from Thompson Creek
Metals Company Inc. (51 %) and Cygnus Mines Ltd. (49 %)

HP, Nod, Selwyn, Falcon & Wolfman Claims
Owned 100% by Selwyn Chihong Mining Ltd.

NTS 105I/05, 06, 11 and 12
6922000N to 6955000N and 445000E to 500000E UTM Zone 9+NAD 83

In the Watson Lake Mining District, Yukon Territory

Prepared by:

Jelle De Bruyckere, M.Sc.

June 2011

Table of Contents

	Page
1. Introduction	1
1.1. Property Status	1
1.2. Location, Access and Infrastructures	2
1.3. Physiography and Climate	5
1.4. Property History	5
1.5. Description of Undertakings	8
1.5.1. Surficial Undertakings	8
1.5.2. Drilling	8
1.6. Regional Geology and Metallogeny	10
1.7. Local Geology and Metallogeny	11
 2. List of Claims	 14
 3. Drilling	 15
4.1. Drill Collar Locations	15
4.2. Drill Core Geology	15
4.2.1. XY Central Deposit	15
4.2.2. XY West Deposit	24
4.3. Sample Preparation, Analysis and Security	26
4.3.1. Analytical Procedures	26
4.3.2. Security and Chain of Custody	26
4.3.3. QA/QC Program	26
 5. Summary and Recommendations	 28
5.1. Surficial	28
5.2. Drilling and Interpretations	28
 6. References	 29

FIGURES

Figure 1	Location map of the Selwyn Property	1
Figure 2	Selwyn Project – 2010 XYC & XYW Drill Collars	map pocket
Figure 3	Selwyn Project – Claim Names and Locations	map pocket

TABLES

Table 1	Summary of diamond drilling	7
Table 2	Collar Locations	9
Table 3	Stratigraphy of Selwyn Property	12
Table 4a	Summary of claims optioned by Selwyn Chihong	14
Table 4b	Summary of claims 100% owned by Selwyn Chihong	15
Table 5	Mineralized Intercepts XY Central Deposit	21-24
Table 6	Mineralized Intercepts XY West Deposit	25

PLATES

Plate 1	Mineralized Active member	13

APPENDICES

<i>A - Statement of Expenditures</i>	33
<i>B - Statement of Qualifications</i>	35
<i>C - Cross Sections and Detailed Drill Hole Location Maps</i>	
<i>D - Drill logs</i>	
<i>E - Certificates of Geochemical Analyses</i>	

1. Introduction

1.1. Property Status

The Selwyn Project is located on the border between Yukon Territory and Northwest Territories within the larger Selwyn Basin (Figure 1). The majority of the project is located in the Yukon, and the entire Yukon portion of the project is in the Watson Lake Mining District (except for the 29 River claims, which are located in the Whitehorse Mining District, covering the filter plant area). The Yukon portion of the project comprises 1,055 Quartz Mineral claims (100% owned by Selwyn Chihong Mining Ltd.) covering 19,294 hectares and 420 Quartz Mineral claims (under option from Thompson Creek Metals Company Inc. and Cygnus Mines Ltd.) covering 7,450 hectares (Figure 2). These claims do not include the 122 ‘hydro claims’ (Jakal & Igloo Quartz Mineral claims, 100% owned by Selwyn Chihong Mining Ltd.) and the 35 ‘filter plant claims’ (River and Way Quartz Mineral Claims, 100% owned by Selwyn Chihong Mining Ltd.). The Northwest Territories portion of the project comprises 5 claims (100% owned by Selwyn Chihong Mining Ltd.) covering 3,373 hectares and 2 leases (under option from Thompson Creek Metals Company Inc.) covering 2,162 hectares.

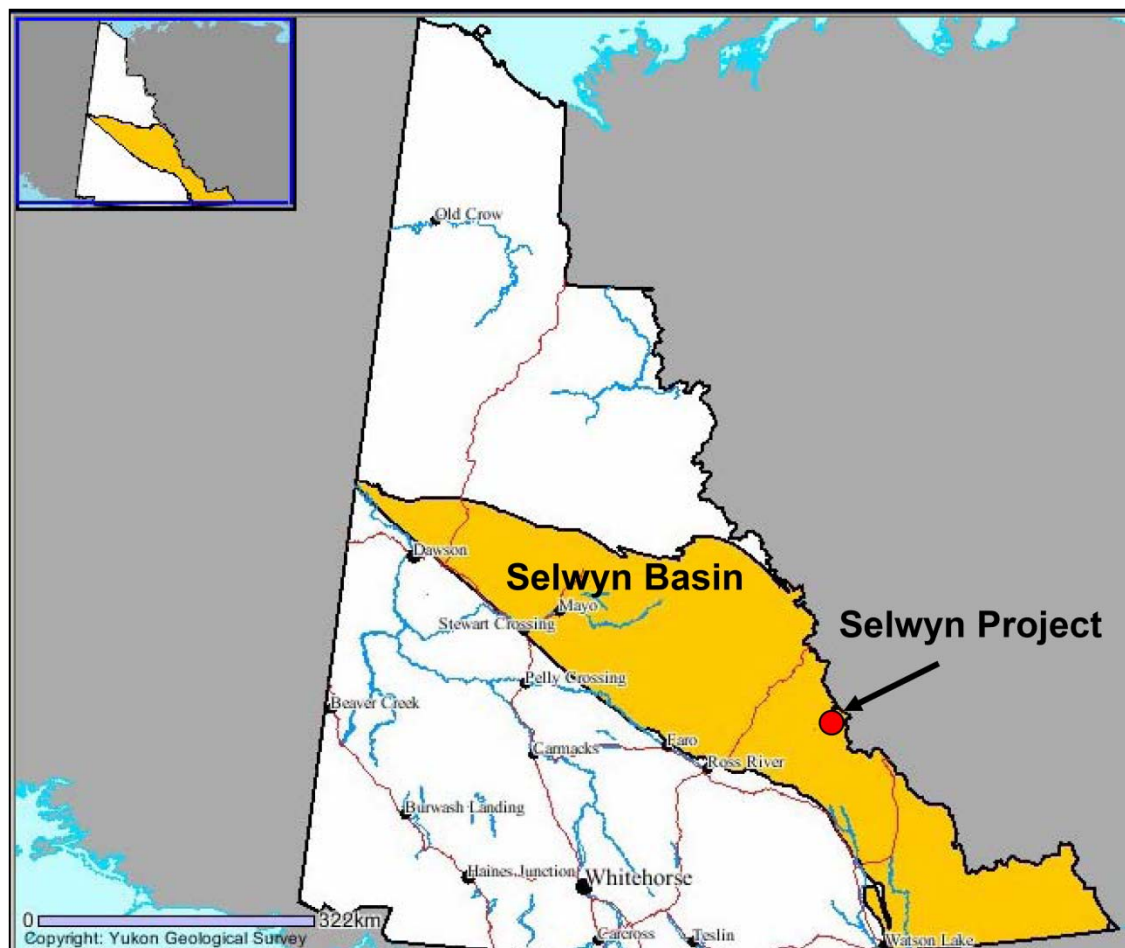


Figure 1: Location map; modified from Yukon Geological Survey website:

<http://maps.gov.yk.ca/imf.jsp?site=YGS>.

On August 18, 2005, Pacifica Resources Ltd. (“Pacifica”) entered into an agreement to acquire 100% of the Howard’s Pass Joint Venture property (referred to subsequently as “Selwyn Project”) in the Yukon Territory and Northwest Territories from Placer Dome (CLA) Ltd. (“Placer”) and Cygnus Mines Ltd. (“Cygnus”), a subsidiary of US Steel Corporation. Note that with the takeover of Placer, the interest of Placer was transferred to Terrane Metals Corp. (“Terrane”); until Terrane got taken over by Thompson Creek Metals Company Inc. (“Thompson”) on 20 October 2010. This acquisition provides Pacifica 100% ownership, subject to the royalty and net profits interest, with no back-in rights to participation in the project by either Thompson or Cygnus. More details can be found in the August 22, 2005 Pacifica press release (www.selwynresources.com).

On June 7, 2007, Pacifica Resources Ltd. changed its name to Selwyn Resources Ltd. (“Selwyn”). All Pacifica’s non-Selwyn District, Yukon Territory exploration properties have been transferred to a new exploration company, Savant Explorations Ltd.

On December 15, 2009, Selwyn announced a possible C\$100 million joint venture transaction with Yunnan Chihong Zinc & Germanium Co. Ltd (“Yunnan”). Selwyn executed a binding framework agreement with Yunnan. The parties have agreed to form a joint venture operating company to finance the advancement of the Selwyn project to bankable feasibility, and if warranted, to production. Full details can be found in the December 14, 2009 Selwyn news release (www.selwynresources.com).

On August 18, 2010, Selwyn closed the CDN\$100 million joint venture transaction with Chihong Canada Mining Ltd (“Chihong”), an indirect wholly owned subsidiary of Yunnan Chihong Zinc & Germanium Co. Ltd., a Chinese company. Pursuant to the Transaction: Selwyn and Chihong incorporated Selwyn Chihong Mining Ltd. (“JVCO”), owned 50/50% by Selwyn and Chihong, to be the operator of the Joint Venture. CDN\$100 million was deposited by Chihong into a JVCO bank account in Canada. These funds will be used to pay for pre-development programs of the Joint Venture. Chihong will earn a 1% interest in the Joint Venture for each CDN\$2 million of the funds spent. Selwyn has transferred all Selwyn Project claims, equipment, permits and licenses to JVCO to be held by it as trustee for Selwyn and Chihong in accordance with their interests in the Joint Venture. Full details can be found in the August 18, 2010 Selwyn news release (www.selwynresources.com).

1.2. Location, Access and Infrastructures

The Selwyn Project claims are a northwest trending strip with the claims in the Yukon being approximately 54 km long by 5 km wide (Figure 2), located approximately 350 km northeast of Whitehorse, Yukon. The property is located at the Yukon Territory and Northwest Territories border between Universal Transverse Mercator (UTM) coordinates 445000E/6955000N in the northwest and 500000E/6922000N in the southeast (UTM Zone 9, NAD83). The property is located on NTS map sheets 105I/05, 06, 11 and 12.

Access to the property for the 2010 field season was by aircraft only. Most materials and supplies used during last year’s exploration season were flown to site by fixed-wing

aircraft from Alkan Air Ltd. and Nomad Air Ltd., both based in Whitehorse, Yukon and Summit Air, based out of Yellowknife. Few supplies came from the remaining 2009 stock present in Don Camp and XY Camp.

A 78 km long NWT exploration all-season access road near Pelly Lakes, built by Placer Dome in 1976-1980, connects the Selwyn Project property to the former town site of Tungsten, NWT. This road requires only minor rehabilitation to be returned to full use. The Nahanni Range Road (Highway 10) connects Cantung with the Robert Campbell Highway. This highway runs from Watson Lake to Carmacks, serves the communities of Faro and Ross River and intersects the Canol Road near Ross River. During early fall of 2010 this road was used to bring in 6 new pieces of heavy equipment.

In June 2008 Selwyn received from the Mackenzie Valley Land and Water Board (NWT) the Land Use Permit (LUP) (MV2005F0028) and a Type B Water License (MV2006L8-0001) for the rehabilitation and use of the all-season access road to the Selwyn Project. The issuance of the LUP and Water License will allow Selwyn to undertake the necessary work to rehabilitate the existing running surface of the road and update bridges and culverts up to current environmental standards; thereby once again allowing all-season road access to the Selwyn Project for the transport of heavy equipment and supplies.

The JVCO is now in a legal position to use the road, after Selwyn having submitted two operational plans which were both approved by the Mackenzie Valley Land and Water Board: a Wildlife Protection Plan (required under the Land Use Permit) and an Abandonment and Restoration Plan (required under the Type B Water License).

Selwyn received a Class A land use permit (S07C-003) on October 14 2009 from the Sahtu Land and Water Board of the Northwest Territories. The permit, which is valid for a period of five years, will allow us to carry out diamond drilling (up to 100 drill holes) on its mining claims and leases in the Northwest Territories.

The JVCO received in July of 2010 an amended Mining Land Use Permit (LQ00250b). This permit provides authorization for much of the work required for new project infrastructure for the planned advanced exploration underground program at Selwyn. Receipt of this amended permit from Yukon Government Energy, Mines & Resources ministry, allows immediate commencement of work on new infrastructure such as upgrades to drill and access roads, expansion of camp up to 160 persons, additional fuel storage, and use of explosives.

The JVCO received on 20 April, 2011 a type B Water License (Q210-042) for the Selwyn Project. The license was issued by the Yukon Water Board and allows for the use and discharge of water related to the proposed initial underground development activities at the XY Central deposit. The type B Water License, issued following an assessment of the underground program at the Selwyn Project by the Yukon Environmental and Socio-economic Assessment Board (YESAB), has a 10-year term. Together with the amendment to Selwyn Chihong's Land Use Permit, it allows for the immediate commencement of required portal, maintenance and waste storage facilities

required for the planned underground program to access the XY Central deposit. The license establishes conditions for a rock stockpile storage facility, ponds and facilities for treatment of mine waters, new roads, expansion of camp facilities, additional fuel storage, and the use of explosives.

Infrastructure on the property is concentrated around three camp areas: XY, Anniv and Don (Figure 2). XY and Anniv were used by Placer in the 1970's and 80's. Both camp areas have an airstrip and a wooden building left by Placer. XY Camp was built by Pacifica in 2006, and consists of 20 tents accommodating up to 50 people. It was used during the 2006, 2007, 2009 and 2010 exploration program. Anniv Camp was built by Pacifica in 2005, and consisted of 20 tents accommodating up to 50 people. It was used during the 2005 and 2006 exploration programs and during 2 summer months in 2007. This camp has been moved to the Don Valley and is now known as Don Camp. Don Camp is built by Pacifica in the fall of 2006 and spring of 2007. It consists of 35 tents and can accommodate up to 60 people. It was used during the 2007, 2008 and 2010 exploration program and temporarily during 2009's start-up. It has a large workshop and a 1,025 m (3360') long by 30 m (100') wide airstrip with turnaround at both ends, which allows planes as big as the DHC-5 Buffalo to land and take off.

Before the fall of 2010, the heavy equipment machines on site included a D7H, a D7G, a D5, a D3, a 320 excavator, two 420 backhoe loaders and two Kenworth dump trucks. This equipment was used in the construction of the 1 km long Don airstrip and in the construction and rehabilitation of the 23 km long dirt trail between XY and Don Camp. In 2007 approximately 4 km of this trail was built, the remaining 19 km was rehabilitated. The trail allows us to drive ATV's, 6x6 Rangers, pickup trucks and small dump trucks from one camp to the other one. A 3.5 km long trail to the Don deposit was also built in 2007. Thanks to the major trails and multiple CAT trails in the Anniv Central, Don, Don East, XYC and XY West deposits most of the drilling is accessible by trail. In the fall of 2010 six new pieces of heavy equipment were driven to the project site along the NWT exploration all-season access road. These included: 1 CAT 730 rock truck (6 wheel drive, 30 ton), 1 CAT 966 front end loader (rubber tires), 1 CAT D8T bulldozer (came with 2 blades), 1 CAT 345 excavator (40 ton), 1 CAT 525 skidder (with winch and grapple) and 1 dual axle trailer.

During the 2008 exploration season the existing trails got improved, some parts got widened, several shortcuts were made, some hills were made less steep, the newly built Don Bridge was relocated to a better spot, a new small bridge was built and more culverts were put in place.

During the 2009 exploration season a new 3 km long dirt trail was built from the XY ore piles to the main trail, converging 1.5 km west-northwest of the XY West Deposit. This new section shortened the trail between Don Camp and XY Camp by 1.2km. A new bridge was built on this road, just east of the portal area. Closer to Don Camp another shortcut was made. Preparations for the portal area commenced late in the season.

During the 2010 exploration season existing trails in the XYC, XYW and DON area were rehabilitated as well as new drill access trails were made. Steep hills were flattened where possible or avoided by moving the trail. The section of road near the 'clay hill' got decommissioned and the land was reclaimed. A new stretch of road was built on top of eskers, north of the old road.

1.3. Physiography and Climate

The physiography of the area consists of U-shaped glacial valleys culminating in rounded peaks. Elevation on the property varies from 1125m at Pelly River to 2035m at Yara Peak. The slopes are steep, talus covered; culminating into rounded tops. Outcrops are sparse and occur on the peaks and along streams flowing down into the Pelly River and Don River. The rivers are part of the Yukon River Watershed.

Climate on the property consists of cold, long winters and cool, short summers. Temperature varies from -40°C in the winter to 25°C in the summer. Snow accumulation in winter is 2-2.5m. Thawing commences in May and the property is bare of snow by late June (Burgoyne 2005).

1.4. Property History

The core claims to the Selwyn Project that were staked by Placer at the beginning of 1972, are now under option from Thompson and Cygnus. Placer conducted mapping, surficial geochemical sampling and diamond drilling on the property, defining significant stratiform Zn-Pb mineralization in two main deposits, XY and Anniv, and a mineralized zone, OP. In 1975 Cygnus purchased a 49% interest in the property from Placer. The joint venture conducted further surface exploration work, and in 1980-81 conducted an underground exploration program. The initial economic evaluation of the property in 1982 resulted in the project being placed on standby by the joint venture. Claims outside the immediate areas of known mineralization were allowed to lapse.

In 1998, Expatriate Resources Ltd. ("Expatriate") purchased a 100% interest in the HP and NOD claims, which were originally staked in 1994, from United Keno Hills.

In 2000, Copper Ridge Explorations Inc. ("Copper Ridge") entered into an option agreement with Placer and Cygnus to acquire the Howard's Pass property. Copper Ridge drilled eight diamond drill holes, but allowed their option agreement to expire.

In the summer of 2004, Expatriate conducted prospecting and surficial geochemical sampling on their HP and NOD claims. In December of 2004, Pacifica was spun off from Expatriate and assumed 100% ownership of the HP and NOD claims.

In 2005, Pacifica entered into an option agreement with Placer and Cygnus to purchase 100% ownership of the Howard's Pass property. That same year Pacifica staked the Selwyn 1-535 claims, to the west, north and east of Pacifica's already-existing claims and the claims optioned from Placer and Cygnus.

In 2006 Pacifica staked 258 claims (Selwyn 536-793) to the north-northwest of the existing claims to cover the historical “Abbey” showing (Figure 3). Also in 2006, Placer’s interest in their claims was transferred to Goldcorp Inc., and then to Terrane.

In 2007 Pacifica changed its name to Selwyn Resources Ltd (“Selwyn”). Another 100 claims (Selwyn 794-893) located south of the area between OP and Anniv Central were staked by Selwyn.

In 2008 Selwyn kept all its existing claims in good standing. In October, 14 additional NOD claims (NOD 67 to NOD 78, NOD 85 and NOD 86) were staked by Coureur des Bois.

Early 2009 David Legault and Gabe Xue went out to the field to stake 7 additional NOD claims: NOD79 to NOD85. Note that an error occurred in the naming of the claims. NOD85 should have been named NOD87. A correction to NOD87 was made with the Yukon Mining Recorder. Another 122 claims were staked in 2009 as well. These are the Jakal and Igloo claims, also known as the ‘hydro claims’.

In 2010 the JVCO kept all its existing claims in good standing. A total of 35 claims were staked in 2010 to cover the filter plant location. These are the River and Way claims.

Drilling activities since the initial discovery are summarized by year and ownership in Table 1 (see next page).

Period	Company	Grid	Type	Holes	Feet	Metres
1973-1981	Placer Development	ANNIV*	Surface	64	37,606.6	11,462.5
		OP	Surface	9	2,798.6	853.0
		XY	Surface	102	73,448.2	22,387.0
		XY	Underground	35	3,061.0	933.0
			SUBTOTAL	210	116,914.4	35,635.5
2000	Copper Ridge Explorations	ANNIV*	Surface	8	2,356.3	718.2
			SUBTOTAL	8	2,356.3	718.2
2005	Pacifica Resources	ANNIV CENTRAL	Surface	12	3,776.6	1,151.1
		ANNIV EAST	Surface	10	4,000.3	1,219.3
		OP	Surface	4	2,192.9	668.4
		XY	Surface	6	2,568.9	783.0
		DON	Surface	8	5,889.1	1,795.0
		BRODEL	Surface	10	6,392.7	1,948.5
		HP	Surface	3	2,367.5	721.6
			SUBTOTAL	53	27,188.0	8,286.9
2006	Pacifica Resources	PN	Surface	7	4,719.5	1,438.5
		OP	Surface	6	3,016.4	919.4
		EP	Surface	1	375.0	114.3
		ANNIV CENTRAL	Surface	53	37,081.0	11,302.3
		ANNIV EAST	Surface	36	21,327.1	6,500.5
		DON	Surface	42	27,903.9	8,505.1
		BRODEL	Surface	1	507.5	154.7
		HP	Surface	1	596.1	181.7
		XY	Surface	44	36,023.6	10,980.0
			SUBTOTAL	191	131,550.2	40,096.5
2007	Selwyn Resources	DON	Surface	20	30,239.8	9,217.1
		DON EAST	Surface	51	50,709.0	15,456.1
		HC WEST	Surface	15	11,449.5	3,489.8
		HC	Surface	1	2,689.0	819.6
		XY CENTRAL	Surface	18	25,214.6	7,685.4
		Exploration	Surface	2	1,110.2	338.4
			SUBTOTAL	107	121,412.1	37,006.4
2008	Selwyn Resources	DON EAST	Surface	4	4,982.0	1,518.5
		XY WEST	Surface	9	7,671.9	2,338.4
			SUBTOTAL	13	12,653.9	3,856.9
2009	Selwyn Resources	XY WEST	Surface	9	13,236.5	4,034.5
		XYC-151D**	Surface	N/A	586.0	178.6
			SUBTOTAL	9	13,822.5	4,213.1
2010	Selwyn Chihong Mining	XY WEST	Surface	7	11,122.4	3,390.1
		XY CENTRAL	Surface	45	44,753.3	13,640.8
			SUBTOTAL	52	55,875.7	17,030.9
			TOTAL	643	481,773.0	146,844.4

Table 1: Summary of diamond drilling on the Selwyn Project since 1973. Note that for 2010 solely the drill holes that were filed for assessment are listed. (*Combines ANNIV Central and ANNIV East. **Deepening of an existing hole, therefore it's not considered as a new hole.)

1.5. Description of Undertakings

1.5.1. General

All of 2010's exploration activities on the Selwyn Project occurred between late May and mid December. In May the first crew mobilized to Don Camp by helicopter. After most snow in camp and on the airstrip was cleared, more people were sent to Don Camp by fixed-wing aircraft. XY Camp opened up in the first half of September, to accommodate the Cyr Drilling crews. Both Don Camp and XY Camp were put on care and maintenance for 2 weeks during the holiday period, to allow for a smooth and efficient start of the 2011 season.

No Limit Drilling, based out of Don Camp, commenced drilling on June 13 on drill hole ANE-184. They first drilled 2 condemnation holes just north of the Anniv East Deposit where a Tailings Site Facility and Mill Site has been proposed and then 1 condemnation drill hole in the Don Valley where a Tailings Site Facility has been proposed. After that, No Limit commenced drilling in the XY Central Deposit, as part of the infill drilling program. Cyr Drilling, based out of XY Camp, began drilling on September 19 in the XY Central Deposit on hole number XYC-211. Both drilling companies began initially with 1 drill and gradually added 2 drills each. In November No Limit moved all 3 of its drills to the Don Deposit, where another infill drilling program was planned. Cyr moved 2 of its drills to the Don Deposit, while 1 drill was sent to the XY West Deposit. Both drilling companies continued drilling until the first half of December, when drills started to shut down gradually for the holidays.

Don Camp served as a support base for all geological staff, the No Limit drilling crew, most of the heavy equipment operators, the environmental crew, consultants and general camp staff. XY Camp served mainly as a support base for the Cyr Drilling crew, 1 or 2 heavy equipment operators and camp staff. Throughout the season, a Bell 206LR LongRanger and/or a Bell 407 from Heli Dynamics was/were stationed at Don Camp. The heavy equipment was used to build and maintain trails, keep the trails and airstrip snow free and to support the drilling.

1.5.2. Drilling

A total of 7 drills operated on the Selwyn Project in 2010. No Limit Drilling had 3 drills turning on the Selwyn Project between June 13 and December 14. Cyr Drilling had also 3 drills between 19 September and 13 December. Foundex Drilling had 1 drill on the property from early July to mid September. A total of 104 drill holes were drilled in 2010, of which 52 are being filed in this assessment report (Figure 2; Table 1 & Table 2). Of those 104 drill holes, 15 were geotech drill holes drilled by Foundex, the rest were diamond drill holes drilled by No Limit and Cyr, either as condemnation, definition or exploration. All core is stored at Don Camp. Objectives of the drilling program were: 1) Infill drilling to prove up the resources at the XY Central Deposit and the Don Deposit. 2) Geotechnical drilling as preparation for the rock mechanics study and planning of the underground development. 3) Exploration drilling at the XY West Deposit.

Hole ID	Type	UTM (E)	UTM (N)	Elevation (m)	True Azimuth	Hole Angle	Length (m)
XYC-190	Infill	488601.0	6926655.2	1636.2	15.0	-83.0	469.4
XYC-191	Infill	488331.4	6926618.5	1558.5	185.0	-67.0	175.3
XYC-192	Infill	488542.9	6926580.6	1611.9	185.0	-76.5	450.5
XYC-193	Infill	488863.4	6926424.1	1651.7	182.5	-84.0	279.5
XYC-194	Infill	488696.8	6926530.2	1632.1	210.0	-83.0	309.7
XYC-195	Infill	488433.8	6926687.8	1585.3	210.0	-87.0	362.7
XYC-196	Infill	488488.4	6926813.2	1645.9	50.0	-85.0	579.7
XYC-197	Infill	488296.2	6926778.5	1576.3	193.0	-77.5	313.2
XYC-198	Infill	488725.2	6926773.3	1727.7	230.0	-90.0	561.6
XYC-199	Infill	489172.4	6926169.1	1611.4	208.0	-75.0	189.0
XYC-200	Infill	489067.2	6926361.0	1647.0	223.0	-78.0	255.4
XYC-201	Infill	489228.3	6926256.3	1625.4	210.0	-66.0	185.0
XYC-202	Infill	488953.6	6926567.7	1687.8	216.0	-71.0	394.1
XYC-203	Infill	489069.8	6926570.3	1700.7	210.0	-77.0	399.7
XYC-204	Infill	488951.4	6926565.4	1687.7	30.0	-82.0	442.3
XYC-205	Infill	488416.0	6926726.0	1585.0	25.0	-85.0	416.1
XYC-206	Infill	488951.2	6926567.7	1689.0	335.0	-82.0	445.4
XYC-207	Infill	488416.0	6926726.0	1585.0	335.0	-75.0	470.9
XYC-208	Infill	488828.0	6926764.0	1760.0	200.0	-86.5	548.9
XYC-209	Infill	488628.5	6926782.0	1703.3	15.0	-85.0	583.5
XYC-210	Infill	488496.0	6926586.0	1604.0	34.0	-85.0	335.1
XYC-211	Infill	489045.8	6926159.9	1607.2	205.0	-65.0	293.0
XYC-212	Infill	488980.0	6926421.0	1654.0	210.0	-72.0	297.1
XYC-213	Infill	488350.0	6926635.0	1562.0	30.0	-87.0	273.7
XYC-214	Exploration	487284.0	6927260.0	1417.0	40.0	-69.0	248.5
XYC-215	Exploration	487284.0	6927260.0	1417.0	33.0	-71.0	432.2
XYC-216	Infill	488967.7	6926197.6	1608.5	210.0	-68.0	218.0
XYC-217	Infill	488237.0	6926658.0	1522.0	203.0	-70.0	135.5
XYC-218	Infill	488214.0	6926731.0	1535.0	210.0	-65.0	195.3
XYC-219	Infill	488218.0	6926810.0	1574.0	0.0	-87.0	354.2
XYC-220	Exploration	487502.6	6927240.2	1486.2	40.0	-72.0	281.5
XYC-221	Infill	489137.0	6926297.0	1634.0	210.0	-80.0	194.0
XYC-222	Infill	488514.0	6926438.0	1564.0	210.0	-65.0	147.2
XYC-223	Exploration	487394.3	6927161.6	1420.9	28.0	-59.0	650.1
XYC-224	Infill	488938.0	6926346.0	1647.0	210.0	-65.0	213.2
XYC-225	Exploration	487502.6	6927240.3	1486.2	38.5	-65.0	654.4
XYC-226	Infill	488549.0	6926387.0	1568.0	204.0	-84.0	125.8
XYC-227	Infill	488662.9	6926458.6	1625.8	210.0	-83.0	114.0
XYC-228	Infill	488801.1	6926401.4	1639.7	215.0	-85.0	231.2
XYC-229	Infill	488768.9	6926229.2	1583.8	210.0	-70.0	236.0
XYC-230	Infill	488768.2	6926226.1	1583.7	46.0	-85.0	176.0
XYC-231	Infill	488663.0	6926459.0	1625.7	204.0	-75.0	259.5
XYC-232	Infill	489009.5	6926167.2	1603.8	210.0	-80.0	179.0
XYC-233	Exploration	487394.3	6927161.6	1420.9	23.0	-63.0	719.1
XYC-234	Infill	489100.0	6926148.5	1608.3	187.0	-66.0	188.0
XYC-235	Infill	488698.4	6926265.5	1574.1	213.0	-80.0	168.5
XYC-236	Infill	489100.0	6926149.1	1608.2	180.0	-86.0	177.6
XYC-237	Exploration	487502.4	6927241.7	1486.1	137.0	-86.0	404.3
XYC-238	Infill	487925.7	6926795.8	1491.6	75.0	-50.0	332.0
XYC-239	Infill	488887.5	6926191.5	1594.2	210.0	-70.5	221.0
XYC-240	Infill	488887.8	6926191.8	1594.1	224.0	-85.0	194.0
XYC-241	Exploration	489614.0	6926660.0	1628.0	180.0	-74.0	550.0

Table 2: Collar locations and associated information of the drill holes filed for assessment.

1.6. Regional Geology and Metallogeny

The Selwyn property is situated within the Selwyn Basin (Figure 1), a northwest trending basin that accumulated sediments from Cambrian-Ordovician to Lower Devonian (Gordey and Anderson 1993). The Selwyn Basin stretches from the Yukon-Alaska border to northeast British Columbia and is bounded to the north and east by the Mackenzie Platform, to the south by Macdonald Platform and to the west by the Cassiar Platform and the Tintina fault zone. The Selwyn Basin represents a trough at the west margin of a Late Proterozoic continent overlain by rift clastics of Late Devonian age (Gordey and Anderson 1993).

The basement rocks of the Selwyn Basin consist of Upper Proterozoic clastic sedimentary rocks of the Windermere Supergroup. Windermere rocks are overlain by Cambrian-Ordovician carbonate rocks of the Rabbitkettle Formation, overlain in turn by cherts and shales of the Road River Group (Ordovician-Silurian) and chert and black clastic rocks of the Earn Group (Devono-Mississippian; Goodfellow 2004). Mafic volcanic rocks also occur within the Selwyn Basin as discontinuous, lenticular belts that parallel riftbounding faults or as isolated volcanic piles (Goodfellow 2004). A set of Mid-Cretaceous granitic and granodioritic plutons intrude sedimentary rocks located northeast of the Tintina Fault and are termed the Selwyn Plutonic Suite (Gordey and Anderson 1993).

Regionally, strata in the Selwyn Basin are folded about west-northwest-trending axes that plunge to the northwest (Goodfellow and Jonasson 1987). Several thrust faults are interpreted in the area surrounding the Selwyn property; the March, Appler, Sapper, and Honeymoon Faults are generally trending northwest-southeast, dip to the southwest, and are attributed to shortening of the basin (Gordey and Anderson 1993).

Bedding is easily identified on outcrop by the contrast between the shale and limestone beds and due to recessive weathering of specific beds. The bedding dominantly strikes northwest and dips gently to moderately southwest. A pervasive, regional slaty cleavage strongly overprints the bedding. Cleavage spacing ranges from mm to cm intervals and is better developed in the shales. The cleavage strikes northwest and is steeply dipping to the northeast. The intersection lineation between bedding and cleavage gently plunges northwest.

The rocks of the Selwyn Basin are host to numerous Zn-Pb sedimentary-exhalative ("SEDEX") deposits. The mafic volcanic rocks in the basin are significant in that there appears to be a close temporal and/or spatial relationship between volcanic centres and SEDEX deposits (Goodfellow 2004). This relationship, however, is not seen at the Selwyn Project. There are four main SEDEX districts in the Selwyn Basin: 1) Gataga (Cirque and South Cirque deposits) in northeastern BC, 2) MacMillan Pass (Jason and Tom deposits) in the southeastern Yukon, 3) Anvil (Vangorda, Faro, Grum, Dy and Swim deposits) near Faro, Yukon, and 4) Howard's Pass (Selwyn property; Section 1.7, below). These deposits range in age from Early Cambrian to Late Devonian (Goodfellow 2006).

In addition to SEDEX-style Zn-Pb deposits, the Selwyn Basin also contains world-class deposits of barite and tungsten (Gordey and Anderson 1993). Tungsten is found in skarn deposits, which also can contain Zn, Pb, Cu, Mo, and Sn.

1.7. Local Geology and Metallogeny

Using predominantly field observations, Gordey and Anderson (1993) subdivided the stratified rocks in the region around the Selwyn property (the Nahanni map-area; NTS map sheet 105I) into 31 distinct formations, only 7 of which are found in the immediate vicinity of the Selwyn Project (Table 3). From youngest to oldest, the formations include:

1. Selwyn Plutonic Suite:

- Intrusive stocks and batholiths, ranging in composition from intermediate to granitic.

2. Prevost Formation: thickness estimated at 900m, subdivided into three members.

- *Upper member:* coarse-grained, poorly sorted chert-quartz sandstone and conglomerate in thick beds; clasts in the conglomerate are 75% whiter sandstone and 25% gray chert; unit is 300m thick.
- *Middle member:* brown weathering, dark gray, thin bedded shale and siltstone; unit is 90m thick.
- *Lower member:* grey weathering, dark grey, medium- to coarse grained chert-quartz sandstone; unit is 160m thick.

3. Portrait Lake Formation: thickness at the type location is 897m, subdivided into three members.

- *Upper member:* gun-blue weathering, black platy siltstone; unit is 260m thick; an extensive barite horizon can be observed near the upper contact.
- *Middle member:* black weathering, massive pebble conglomerate; clasts composed of chert and siliceous argillite; unit is 195m thick.
- *Lower member (Backside Siliceous Mudstone member):* dark brown weathering, silty shale and shale in beds; unit is 420m thick.

4. Steel Formation: thickness 140m.

- *Flaggy mudstone:* orange weathering member consists of siliceous argillite in beds, 10-80cm thick, with wispy laminations.

5. Howard's Pass Formation (Duo Lake Formation): estimated thickness 300m, subdivided into five members.

- *Upper Siliceous Mudstone member:* interlaminated dark grey to grayish black mudstone with medium grey chert, abundant limestone concretions when Active member occurs below, 1m thick zone of graptolites near the top.

- *Active member*: repetitive sequence of intercalated carbonaceous mudstone, cherty mudstone, chert and limestone and locally contains economically significant Zn and Pb sulphides (Morganti 1979).
- *Lower Cherty Mudstone member*: monotonous, slightly bedded, very carbonaceous, blocky siliceous mudstone, up to 30% quartz vein 'pseudobeds' (mimicking layers), up to 1% pyrite nodules.
- *Calcareous Mudstone member*: massive monotonous, calcareous, carbonaceous mudstone, 0.2m graptolite zone, feathery calcite beds with pyritic cores.
- *Pyritic Siliceous Shale member*: fissile siliceous carbonaceous shale with 1-10mm pyrite concretions.

6. Transition Formation: thickness estimated to be 10m; located between the Howard's Pass and the Rabbitkettle Formations; identified locally in drill core by Morganti (1979 and 1982) and Goodfellow and Jonasson (1986).

- Thin interlaminations of grey limestone and buff colored shale, generally well cleaved.

7. Rabbitkettle Formation ("Cambrian Limestone"): has a thickness of 900m.

- *Upper member ("Wavy Banded Limestone")*: intercalated sequence of limestone and calcareous mudstone; wavy banded due to ductility contrasts of the two rock types during deformation.
- *Lower member ("Massive Limestone")*: grey orange weathering, argillaceous to silty limestone, usually in beds less than 10cm.

8. Narchilla Formation (Windermere Supergroup): has a thickness of 820m.

- Maroon to dark blue-grey weathering shale.

Age	Group	Formation	Member
Upper Devonian to Middle Mississippian	Upper Earn	Prevost (Yara Peak)*	
Lower to Upper Devonian	Lower Earn	Portrait Lake (Iron Creek)*	
Upper Silurian	Road River	Steel	Flaggy Mudstone*
Ordovician and Middle Silurian		Howard's Pass* (Duo Lake)	Upper Siliceous Mudstone*
			Active Member*
			Lower Cherty Mudstone*
			Calcareous Mudstone*
			Pyritic Siliceous Mudstone*
		Transition*	
Cambrian-Ordovician		Rabbitkettle	
Upper Proterozoic and Lower Cambrian		Narchilla	

Table 3: Stratigraphy of the Selwyn property (Subdivisions after Gordey and Anderson 1993 and *Morganti 1979).

The stratigraphic subdivisions of Morganti (1979) are favoured as these are more applicable on the local property scale and as such, will be used henceforth. Units encountered in drill core include rocks from the Rabbitkettle Formation to the Yara Peak formation (Table 3). The stratigraphy on the property strikes roughly 300° and the attitude and dip of structures in the Selwyn property are similar to the regional structures. Several minor faults are observed in drill core and surface expressions of faults are extrapolated from topographic features.

The Zn-Pb mineralization on the Selwyn Project is hosted in Active member of the Howard's Pass Formation. Surface exposures of Active member prove elusive and are difficult to identify as the black shale hosting the mineralization is similar to the other shales observed on the property. However, the Active member is easily recognizable in drill core and consists of alternating layers of carbonaceous mudstone, cherty mudstone, limestone, and chert. The sulphide minerals occur as fine laminations of sulphides that are stratabound, fine-grained and consist dominantly of sphalerite, galena and minor pyrite (Plate 1). Thickness of mineralization ranges from 1.05 to 40.36 m. Pressure dissolution cleavages are observed in higher grade zones and are commonly replaced with secondary sphalerite and galena. In addition, medium- to coarse-grained galena fills tensile fractures in, which are commonly enclosed in calcite veins. The calcite veins are 5-8 cm long and 3-4 cm thick. The tensile fractures are 1-2cm long and 0.5-1cm thick. The highest Zn and Pb grades in the Active member occur in the XY Central deposit and the Don deposit.

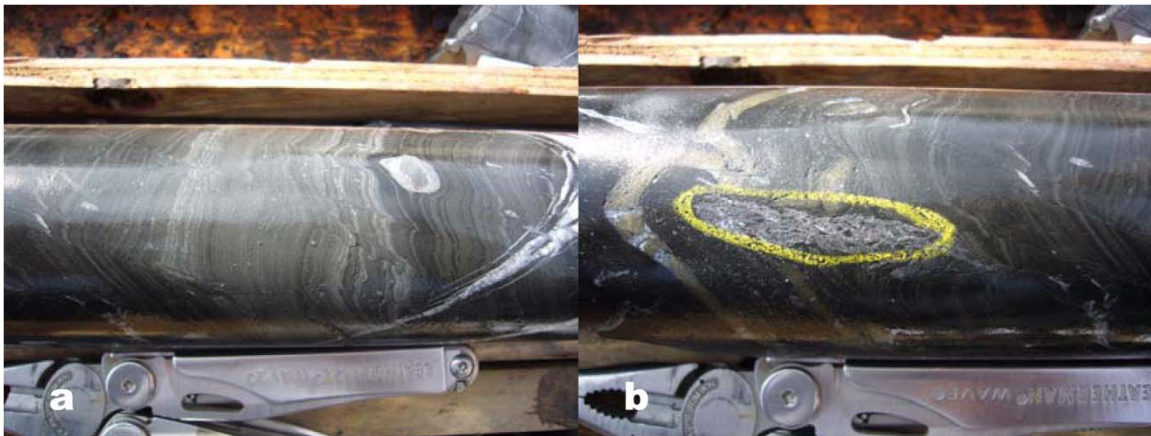


Plate 1: Photo 'a' shows the sulphide laminations in the Active member (lighter bands). Photo 'b' shows a secondary crosscutting galena infill structure (circled in yellow). These samples are from drill hole XYC-138, NQ₂ core size.

2. List of Claims by name and grant number

The following tables (4a & 4b) list all the claims of the Selwyn Project. The claims that got renewed in 2010 are highlighted in gray. Figure 3 shows the location of all claims listed below.

Target Area	Claim Names	Grant Numbers
XY	X1-X29	Y64526-Y64554
	X31	Y 64556
	X33-X35	Y64558-Y64560
	X37-X46	Y64670-Y64679
	X 54	Y73608
R	R1-R8	Y64723-Y64730
	R9-R15	Y64896-Y64902
	R16-R39	Y64680-Y64703
	R40-R47	Y64744-Y64751
	R48-R66	Y64704-Y64722
	R155-R161	Y64760-Y64766
DON	DON1-DON8	Y64845-Y64852
	DON10-DON17	Y64911-Y64918
	DON21-DON28	Y64953-Y64960
	DON29-DON34	Y64929-Y64934
	DON35-DON36	Y64919-Y64920
	DON71-DON76	Y64947-Y64952
	DON77-DON81	Y64961-Y64965
	DON101-DON116	Y64966-Y64981
	DON151-DON164	Y70216-Y70229
	DON240-DON247	YA00771-YA00778
	DON248-DON255	YA00787-YA00794
OP	DON256-DON263	YA11072-YA11079
	DON264-DON267	YA00806-YA00809
	OP1-OP8	Y64837-Y64844
	OP9-OP16	Y64887-Y64894
	OP17-OP20	Y64731-Y64734
	OP21-OP28	Y64767-Y64774
	OP29-OP36	Y64903-Y64910
	OP41-OP54	Y70230-Y70243
	OP101-OP175	Y93875-Y93951
	OP200-OP202	Y94598-Y94600
	OP203-OP207	YA00001-YA00005
	OP208-OP223	Y94482-Y94497
	OP224-OP225	YA00006-YA00007
	OP230-OP235	YA00765-YA00770
ANNIV	OP230-OP235	YA20057-YA20062
	OP236-OP247	YA00449-YA00460
ANNIV	ANNIV1-ANNIV16	Y73582-Y73597
D	D1	YA00379
DJ	DJ	YA00380
	DJ2	YA00381
	DJ5-DJ8	YA00384-YA00387
KNAP	KNAP1-KNAP3	YA00555-YA00557
	KNAP 4	YA25686

Table 4a: Summary of claims optioned by Selwyn Chihong from Thompson CreekMetals Company Inc. & Cygnus Mines Ltd. The claims that got renewed in 2010 are highlighted in gray.

Target Area	Claim Names	Grant Numbers
HP	HP1-HP20	YB46381-YB46400
	HP21-HP31	YB47301-YB47311
NOD	NOD1-NOD66	YB49365-YB49430
	NOD69-NOD78	YC74009-YC74018
	NOD79-NOD84	YC74051-YC74056
	NOD85-NOD86	YC74025-YC74026
	NOD87(85)	YC74057
SELWYN	SELWYN1-SELWYN414	YC27987-YC28400
	SELWYN415	YC28701
	SELWYN416-SELWYN439	YC29223-YC29246
	SELWYN440-SELWYN535	YC29327-YC29422
	SELWYN536-SELWYN793	YC31510-YC31767
	SELWYN794-SELWYN893	YC71661-YC71760
FALCON	FALCON155-FALCON162	YB34094-YB34101
	FALCON163	YB34102
	FALCON164	YB34103
	FALCON165	YB34104
	FALCON166	YB34105
WOLFMAN	WOLFMAN1-WOLFMAN28	YB90963-YB90990
	WOLFMAN29-WOLFMAN34	YB92371-YB92376

Table 4b: Summary of claims owned 100% by Selwyn Chihong. The claims that got renewed in 2010 are highlighted in gray. The Wolfman claims have been paid in lieu.

3. Drilling

3.1. Drill Collar Locations

Fifty two drill holes are being filed for 2010 (Figure 2; Table 2). So far 36 drill collars have been surveyed by a differential GPS and 16 drill collars were located by a handheld GPS. The 16 drill collars will get surveyed by a differential GPS in 2011. Appendix D includes hard copies of drill logs for each hole and shows a more detailed description of each hole. Appendix D includes cross-sections, constructed along the 30° drilling grid, showing all the drill holes.

3.2. Drill Core Geology

3.2.1. XY Central Deposit

DDH XYC-190: Infill drilling in the XY Central deposit. Drill hole depth is 469.4m with NQ3 core size. The drill hole collared in Backside Siliceous Formation which was intersected to a depth of 101.2m; it intersected Flaggy Mudstone from 101.2m to 253.6m, Upper Siliceous Mudstone from 253.6m to 333.6m, Active Member from 333.6m to 419.3m, Calcareous Mudstone from 419.3m to 469.4m; EOH.

DDH XYC-191: Infill drilling in the XY Central deposit. Drill hole depth is 175.3m with NQ3 core size. The drill hole collared in Flaggy Mudstone which was intersected to a depth of 68.7m; it intersected Upper Siliceous Mudstone from 68.7m to 75.4m, a fault from 75.4m to 81.4m, Active Member from 81.4m to 168.1m, a fault from 168.1m to 175.3m; EOH.

DDH XYZ-192: Infill drilling in the XY Central deposit. Drill hole depth is 450.5m with NQ3 core size. The drill hole collared in Backside Siliceous Mudstone which was intersected to a depth of 65.7m; it intersected Flaggy Mudstone from 65.7m to 141.0m, Upper Siliceous Mudstone from 141.0m to 191.7m, Active Member from 191.7m to 223.3m, Calcareous Mudstone from 223.3m to 450.5m; EOH.

DDH XYZ-193: Infill drilling in the XY Central deposit. Drill hole depth is 279.5m with NQ3 core size. The drill hole collared in Backside Siliceous Mudstone which was intersected to a depth of 23.4m; it intersected Flaggy Mudstone from 23.4m to 124.2m, Upper Siliceous Mudstone from 124.2m to 225.2m, Active Member from 225.2m to 231.8m, Calcareous Mudstone from 231.8m to 279.5m; EOH.

DDH XYZ-194: Infill drilling in the XY Central deposit. Drill hole depth is 309.7m with NQ3 core size. The drill hole collared in Backside Siliceous Mudstone which was intersected to a depth of 102.9m; it intersected Flaggy Mudstone from 102.9m to 190.3m, Upper Siliceous Mudstone from 190.3m to 256.2m, Active Member from 256.2m to 270.1m, Calcareous Mudstone from 270.1m to 309.7m; EOH.

DDH XYZ-195: Infill drilling in the XY Central deposit. Drill hole depth is 362.7m with NQ3 core size. The drill hole collared in Backside Siliceous Mudstone which was intersected to a depth of 119.4m; it intersected Flaggy Mudstone from 119.4m to 226.3m, Upper Siliceous Mudstone from 226.3m to 282.0m, Active Member from 282.0 to 321.1m, Calcareous Mudstone from 321.1m to 362.7m; EOH.

DDH XYZ-196: Infill drilling in the XY Central deposit. Drill hole depth is 579.7m with NQ3 core size. The drill hole collared in Backside Siliceous Mudstone which was intersected to a depth of 331.6m; it intersected Flaggy Mudstone from 331.6m to 505.9m, Upper Siliceous Mudstone from 505.9m to 520.9m, a fault from 520.9m to 522.7m, Active Member from 522.7m to 528.4m, Calcareous Mudstone from 528.4m 579.7m; EOH.

DDH XYZ-197: Infill drilling in the XY Central deposit. Drill hole depth is 313.2m with NQ3 core size. The drill hole collared in Backside Siliceous Mudstone which was intersected to a depth of 141.0m; it intersected Flaggy Mudstone from 141.0m to 208.9m, Upper Siliceous Mudstone from from 208.9m to 255.0m, Active Member from 255.0m to 278.6, Calcareous Mudstone from 278.6m to 313.2m; EOH.

DDH XYZ-198: Infill drilling in the XY Central deposit. Drill hole depth is 561.6m with NQ3 core size. The drill hole collared in Backside Siliceous Mudstone which was intersected to a depth of 277.6m; it intersected Flaggy Mudstone from 277.6m to 340.1m, a fault from 340.1m to 349.7m, Upper Siliceous Mudstone from 349.7m to 484.6m, Active Member from 484.6m to 531.7m, Calcareous Mudstone from 484.6m to 561.6m; EOH.

DDH XYZ-199: Infill drilling in the XY Central deposit. Drill hole depth is 189.0m with NQ core size. The drill hole collared in Flaggy Mudstone which was intersected to

a depth of 18.9m; it intersected Upper Siliceous Mudstone from 18.9m to 79.7m, Active Member from 79.7m to 104.3m, Calcareous Mudstone from 104.3m to 189.0m; EOH.

DDH XYC-200: Infill drilling in the XY Central deposit. Drill hole depth is 255.4m with NQ core size. The drill hole collared in Backside Siliceous Mudstone which was intersected to a depth of 84.1m; it intersected Flaggy Mudstone from 84.1m to 107.3m, Upper Siliceous Mudstone from 107.3m to 180.1m, Active Member from 180.1m to 200.3m, Calcareous Mudstone from 200.3m to 255.4m; EOH.

DDH XYC-201: Infill drilling in the XY Central deposit. Drill hole depth is 185.0m with NQ core size. The drill hole collared in Backside Siliceous Mudstone which was intersected to a depth of 43.6m; it intersected a fault from 43.6m to 47.3m, Upper Siliceous Mudstone from 47.3m to 133.5m, Active Member from 133.5m to 157.1m, Calcareous Mudstone from 157.1m to 185.0m; EOH.

DDH XYC-202: Infill drilling in the XY Central deposit. Drill hole depth is 394.1m with NQ core size. The drill hole collared in Backside Siliceous Mudstone which was intersected to a depth of 85.7m; it intersected Flaggy Mudstone from 85.7m to 197.4m, Upper Siliceous Mudstone from 194.7m to 335.3m, Active Member from 335.3m to 357.8m, Calcareous Mudstone from 357.8m to 394.1m; EOH.

DDH XYC-203: Infill drilling in the XY Central deposit. Drill hole depth is 399.7m with NQ/NQ3 core size. The drill hole collared in Backside Siliceous Mudstone which was intersected to a depth of 293.8m; it intersected a fault from 293.8m to 316.9m, Upper Siliceous Mudstone from 316.9m to 327.1m, Active Member from 327.1m to 370.4m, Calcareous Mudstone from 370.4m to 399.7m; EOH.

DDH XYC-204: Infill drilling in the XY Central deposit. Drill hole depth is 442.3m with NQ/NQ3 core size. The drill hole collared in Backside Siliceous Mudstone which was intersected to a depth of 442.3m; EOH.

DDH XYC-205: Infill drilling in the XY Central deposit. Drill hole depth is 416.1m with NQ/NQ3 core size. The drill hole collared in Backside Siliceous Mudstone which was intersected to a depth of 105.8m; it intersected Flaggy Mudstone from 105.8m to 235.9m, Upper Siliceous Mudstone from 235.9m to 349.8m, Active Member from 349.8m to 399.1m, Calcareous Mudstone from 399.1m to 416.1m; EOH.

DDH XYC-206: Infill drilling in the XY Central deposit. Drill hole depth is 445.4m with NQ/NQ3 core size. The drill hole collared in Backside Siliceous Mudstone which was intersected to a depth of 131.7m; it intersected Flaggy Mudstone from 131.7m to 215.3m, Upper Siliceous Mudstone from 215.3m to 324.2m, Active Member from 324.2m to 427.2m, Calcareous Mudstone from 427.2m to 445.4m; EOH.

DDH XYC-207: Infill drilling in the XY Central deposit. Drill hole depth is 470.9m with NQ/NQ3 core size. The drill hole collared in Backside Siliceous Mudstone which was intersected to a depth of 61.8m; it intersected Flaggy Mudstone from 61.8m to

84.6m, a fault from 84.6m to 86.5m, Backside Siliceous Mudstone from 86.5m to 127.8m, Flaggy Mudstone from 127.8m to 256.8m, Upper Siliceous Mudstone from 256.8m to 389.6m, Active Member from 389.6m to 434.4m, Calcareous Mudstone from 434.4m to 470.9m; EOH.

DDH XYC-208: Infill drilling in the XY Central deposit. Drill hole depth is 548.9m with NQ/NQ3 core size. The drill hole collared in Iron Creek Formation which was intersected to a depth of 212.4m; it intersected Backside Siliceous Mudstone from 212.4m to 253.6m, Flaggy Mudstone from 253.6m to 369.5m, Upper Siliceous Mudstone from 369.5m to 483.5m, Active Member from 483.5m to 527.1m, Calcareous Mudstone from 527.1m to 548.9m; EOH.

DDH XYC-209: Infill drilling in the XY Central deposit. Drill hole depth is 583.5m with NQ/NQ3 core size. The drill hole collared in Backside Siliceous Mudstone which was intersected to a depth of 280.9m; it intersected Flaggy Mudstone from 280.9m to 460.7m, Upper Siliceous Mudstone from 460.7m to 537.4, Active Member from 537.4m to 555.6m, Calcareous Mudstone from 555.6m to 583.5m; EOH.

DDH XYC-210: Infill drilling in the XY Central deposit. Drill hole depth is 335.1m with NQ/NQ3 core size. The drill hole collared in Backside Siliceous Mudstone which was intersected to a depth of 32.8m; it intersected Flaggy Mudstone from 32.8m to 145.2m, Upper Siliceous Mudstone from 145.2m to 243.0m, Active Member from 243.0m to 289.3m, Calcareous Mudstone from 289.3m to 335.1m; EOH.

DDH XYC-211: Infill drilling in the XY Central deposit. Drill hole depth is 293.0m with NQ/NQ3 core size. The drill hole collared in Flaggy Mudstone which was intersected to a depth of 24.9m; it intersected Upper Siliceous Mudstone from 24.9m to 135.6m, Active Member from 135.6m to 145.7m, Calcareous Mudstone from 145.7m to 293.0m; EOH.

DDH XYC-212: Infill drilling in the XY Central deposit. Drill hole depth is 297.1m with NQ core size. The drill hole collared in Flaggy Mudstone which was intersected to a depth of 112.1m; it intersected Upper Siliceous Mudstone from 112.1m to 212.5m, Active Member from 212.5m to 236.9m, Calcareous Mudstone from 236.9m to 297.1m; EOH.

DDH XYC-213: Infill drilling in the XY Central deposit. Drill hole depth is 273.7m with NQ/NQ3 core size. The drill hole collared in Backside Siliceous Mudstone which was intersected to a depth of 20.5m; it intersected Flaggy Mudstone from 20.5m to 127.6m, Upper Siliceous Mudstone from 127.6m to 204.5m, Active Member from 204.5m to 231.9m, Calcareous Mudstone from 204.5m to 273.7m; EOH.

DDH XYC-216: Infill drilling in the XY Central deposit. Drill hole depth is 218.0m with NQ/NQ3 core size. The drill hole collared in Flaggy Mudstone which was intersected to a depth of 27.8m; it intersected Upper Siliceous Mudstone from 27.8m to 86.0m, Active Member from 86.0m to 114.0m, a fault from 114.0m to 118.1m, Upper

Siliceous Mudstone from 118.1m to 131.7m, Active Member from 131.7m to 168.2m, Calcareous Mudstone from 168.2m to 218.0m; EOH.

DDH XYC-217: Infill drilling in the XY Central deposit. Drill hole depth is 135.5m with NQ/NQ3 core size. The drill hole collared in a fault which was intersected to a depth of 63.9m; it intersected Active Member from 63.9m to 77.9m, Calcareous Mudstone from 77.9m to 102.4m, a fault from 102.4m to 104.1m, Transition Formation from 104.1, to 111.8m, Cambrian Limestone from 111.8m to 135.5m; EOH.

DDH XYC-218: Infill drilling in the XY Central deposit. Drill hole depth is 195.3m with NQ/NQ3 core size. The drill hole collared in Upper Siliceous Mudstone which was intersected to a depth of 119.0m; it intersected Active Member from 119.0m to 125.5m, a fault from 125.5m to 128.7m, Transition Formation from 128.7m to 155.2m, Cambrian Limestone from 155.2m to 195.3m; EOH.

DDH XYC-219: Infill drilling in the XY Central deposit. Drill hole depth is 354.2m with NQ/NQ3 core size. The drill hole collared in Backside Siliceous Mudstone which was intersected to a depth of 44.4m; it intersected Flaggy Mudstone from 44.4m to 260.4m, Upper Siliceous Mudstone from 260.4m to 304.5m, Active Member from 304.5m to 329.2m, Calcareous Mudstone from 329.2m to 354.2m; EOH.

DDH XYC-221: Infill drilling in the XY Central deposit. Drill hole depth is 194.0m with NQ/NQ3 core size. The drill hole collared in Flaggy Mudstone which was intersected to a depth of 80.3m; it intersected Upper Siliceous Mudstone from 80.3m to 148.5m, Active Member from 148.5m to 160.2m, Calcareous Mudstone from 160.2m to 194.0m; EOH.

DDH XYC-222: Infill drilling in the XY Central deposit. Drill hole depth is 147.2m with NQ/NQ3 core size. The drill hole collared in Upper Siliceous Mudstone which was intersected to a depth of 82.6m; it intersected Active Member from 82.6m to 135.8m, Calcareous Mudstone from 135.8m to 147.2m; EOH.

DDH XYC-224: Infill drilling in the XY Central deposit. Drill hole depth is 213.2m with NQ/NQ3 core size. The drill hole collared in Flaggy Mudstone which was intersected to a depth of 82.6m; it intersected Upper Siliceous Mudstone from 82.6m to 163.5m, Active member from 163.5m to 195.5m, Calcareous Mudstone from 195.5m to 213.2m; EOH.

DDH XYC-226: Infill drilling in the XY Central deposit. Drill hole depth is 125.8m with NQ/NQ3 core size. The drill hole collared in Upper Siliceous Mudstone which was intersected to a depth of 97.1m; it intersected Active Member from 97.1m to 124.2m, Calcareous Mudstone from 124.2m to 125.8m; EOH.

DDH XYC-227: Infill drilling in the XY Central deposit. Drill hole depth is 114.0m with NQ core size. The drill hole collared in Backside Siliceous Mudstone which was

intersected to a depth of 17.9m; it intersected Flaggy Mudstone from 17.9m to 97.3m, Upper Siliceous Mudstone from 97.3m to 114.0m; EOH.

DDH XYC-228: Infill drilling in the XY Central deposit. Drill hole depth is 231.2m with NQ/NQ3 core size. The drill hole collared in Flaggy Mudstone which was intersected to a depth of 99.0m; it intersected Upper Siliceous Mudstone from 99.0m to 186.2m, Active Member from 186.2m to 207.3m, Calcareous Mudstone from 207.3m to 231.2m; EOH.

DDH XYC-229: Infill drilling in the XY Central deposit. Drill hole depth is 236.0m with NQ core size. The drill hole collared in Upper Siliceous Mudstone which was intersected to a depth of 127.5m; it intersected a fault from 127.5m to 146.0m, Calcareous Mudstone from 146.0m to 216.9m, a fault from 216.9m to 217.4m, Transition Formation from 217.4m to 236.0m; EOH.

DDH XYC-230: Infill drilling in the XY Central deposit. Drill hole depth is 176.0m with NQ core size. The drill hole collared in Upper Siliceous Mudstone which was intersected to a depth of 69.5m; it intersected Active Member from 69.5m to 87.9m, a fault from 87.9m to 95.2m, Upper Siliceous Mudstone from 95.2m to 122.5m, Active Member from 122.5m to 157.8m, Calcareous Mudstone from 157.8m to 176.0m; EOH.

DDH XYC-231: Infill drilling in the XY Central deposit. Drill hole depth is 259.5m with NQ/NQ3 core size. The drill hole collared in Flaggy Mudstone which was intersected to a depth of 92.6m; it intersected Upper Siliceous Mudstone from 92.6m to 196.8, Active Member from 196.8m to 210.9m, Calcareous Mudstone from 210.9m to 259.5m; EOH.

DDH XYC-232: Infill drilling in the XY Central deposit. Drill hole depth is 179.0m with NQ core size. The drill hole collared in Flaggy Mudstone which was intersected to a depth of 11.6m; it intersected Upper Siliceous Mudstone from 11.6m to 80.8m, Active Member from 80.8m to 98.3m, Calcareous Mudstone from 98.3m to 110.6m, a fault from 110.6m to 112.0m, Upper Siliceous Mudstone from 112.0m to 125.0m, Active Member from 125.0m to 146.2m, Calcareous Mudstone from 146.2m to 179.0m ; EOH.

DDH XYC-234: Infill drilling in the XY Central deposit. Drill hole depth is 188.0m with NQ core size. The drill hole collared in Upper Siliceous Mudstone which was intersected to a depth of 126.6m; it intersected Active Member from 126.6m to 153.3m, Calcareous Mudstone from 153.3m to 188.0m; EOH.

DDH XYC-235: Infill drilling in the XY Central deposit. Drill hole depth is 168.5m with NQ core size. The drill hole collared in Upper Siliceous Mudstone which was intersected to a depth of 67.6m; it intersected Active Member from 67.6m to 148.0m, Calcareous Mudstone from 148.0m to 168.5m; EOH.

DDH XYC-236: Infill drilling in the XY Central deposit. Drill hole depth is 177.6m with NQ core size. The drill hole collared in Upper Siliceous Mudstone which was

intersected to a depth of 71.4m; it intersected Active Member from 71.4m to 112.3m, Calcareous Mudstone from 112.3m to 177.6m; EOH.

DDH XYZ-238: Infill drilling in the XY Central deposit. Drill hole depth is 332.0m with NQ core size. The drill hole collared in Cambrian Limestone which was intersected to a depth of 130.6m; it intersected Calcareous Mudstone from 130.6m to 259.2m, Transition Formation from 259.2m to 292.4m, a fault from 292.4m to 332.0m; EOH.

DDH XYZ-239: Infill drilling in the XY Central deposit. Drill hole depth is 221.0m with NQ core size. The drill hole collared in Upper Siliceous Mudstone which was intersected to a depth of 125.3m; it intersected Active Member from 125.3m to 144.2m, Calcareous Mudstone from 114.2m to 221.0m; EOH.

DDH XYZ-240: Infill drilling in the XY Central deposit. Drill hole depth is 194.0m with NQ core size. The drill hole collared in Upper Siliceous Mudstone which was intersected to a depth of 60.0m; it intersected Active Member from 60.0m to 95.3m, a fault from 95.3m to 116.0m, Active Member from 116.0m to 151.2m, Calcareous Mudstone from 151.2m to 194.0m; EOH.

DDH XYZ-241: Exploration drilling in the XY Central deposit. Drill hole depth is 550.0m with NQ core size. The drill hole collared in Backside Siliceous Mudstone which was intersected to a depth of 309.0m; it intersected Flaggy Mudstone from 309.0m to 373.7m, Upper Siliceous Mudstone from 373.7m to 468.9m, Active Member from 468.9m to 516.2m, Calcareous Mudstone from 516.2m to 550.0m; EOH.

DDH#	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Pb+Zn (%)	True Width (m)
XYZ-190	371.9	402.7	30.8	10.22	4.90	15.13	28.80
Incl.	381.3	383.2	1.9	12.21	2.91	15.12	1.78
Incl.	388.7	391.5	2.8	15.04	4.72	19.76	2.62
Incl.	392.9	402.7	9.8	19.18	11.52	30.71	9.16
Incl.	397.7	401.1	3.4	19.02	15.80	34.82	3.18
XYZ-191	83.0	97.4	14.4	4.04	1.21	5.25	11.42
Incl.	92.4	92.9	0.5	14.93	4.21	19.14	0.40
	108.3	126.8	18.5	7.89	3.37	11.26	14.67
Incl.	108.3	115.7	7.4	11.78	3.62	15.40	5.87
Incl.	118.9	120.9	2.0	10.82	4.50	15.32	1.59
Incl.	122.5	124.0	1.5	13.31	8.85	22.16	1.19
XYZ-192	191.7	195.5	3.8	4.55	0.41	4.96	3.48
	202.7	210.9	8.2	5.58	1.35	6.93	7.52
Incl.	202.7	204.5	1.8	10.33	2.40	12.73	1.65
Incl.	207.8	210.9	3.1	6.09	0.74	6.83	2.84
XYZ-193	153.6	154.4	0.8	7.69	0.95	8.64	0.70
	223.3	227.7	4.4	9.71	1.71	11.42	3.85
Incl.	225.5	226.9	1.4	22.50	9.31	31.81	1.23
XYZ-194	256.2	265.3	9.1	4.77	1.13	5.90	8.96
Incl.	256.2	258.3	2.1	7.88	1.79	9.67	2.07
Incl.	263.1	265.3	2.2	7.44	2.10	9.54	2.17
XYZ-195	282.4	303.0	20.6	9.11	2.67	11.78	16.06
Incl.	288.2	289.8	1.6	10.77	2.16	12.92	1.25
Incl.	292.5	303.0	10.5	11.88	3.20	15.08	8.19

Incl.	293.6	295.0	1.4	26.75	5.21	31.96	1.09
Incl.	300.2	302.5	2.3	22.28	5.43	27.71	1.79
Incl.	300.2	301.7	1.5	27.44	7.58	35.02	1.17
XYC-196	516.6	517.5	0.9	10.83	0.99	11.82	0.84
XYC-197	255.4	269.8	14.4	5.36	1.63	6.99	10.43
Incl.	255.4	258.6	3.2	6.69	2.03	8.72	2.32
Incl.	262.4	269.8	7.4	6.94	2.15	9.09	5.36
Incl.	267.3	269.8	2.5	11.37	3.28	14.65	1.81
XYC-198	383.4	385.8	2.4	6.98	0.36	7.34	2.18
	396.8	397.9	1.1	12.90	0.30	13.20	1.00
	484.6	490.5	5.9	8.58	2.47	11.05	5.36
Incl.	488.9	490.5	1.6	16.66	4.96	21.62	1.45
	501.7	517.7	16.0	6.86	2.02	8.88	14.54
Incl.	507.1	510.5	3.4	7.29	2.18	9.47	3.09
Incl.	515.1	517.7	2.6	21.25	5.89	27.14	2.36
XYC-199	82.7	91.6	8.9	6.89	2.47	9.36	7.94
Incl.	82.7	85.8	3.1	9.84	2.56	12.40	2.77
Incl.	88.8	91.6	2.8	9.51	4.57	14.08	2.50
XYC-200	180.1	188.2	8.1	0.74	2.46	3.20	-
XYC-201	133.5	133.9	0.4	10.02	1.42	11.44	0.38
	139.8	141.2	1.4	5.54	1.46	7.00	1.33
XYC-202	335.3	350.5	15.2	5.24	1.94	7.18	14.86
Incl.	335.3	343.5	8.2	6.02	2.67	8.69	8.02
Incl.	338.2	341.9	3.7	8.14	2.09	10.23	3.62
XYC-203	328.7	350.0	21.3	5.30	1.95	7.25	19.48
Incl.	329.6	335.4	5.8	7.40	3.09	10.49	5.30
Incl.	330.1	332.2	2.1	9.93	5.40	15.33	1.92
XYC-204	Nil - No ACTM at target depth and no fault intercepted, hole abandoned in HW rock						
XYC-205	349.7	354.3	4.6	7.93	1.85	9.78	4.18
	362.1	374.1	12.0	5.36	1.02	6.38	10.91
Incl.	368.9	374.1	5.2	7.41	1.44	8.86	4.73
Incl.	378.6	380.4	1.8	8.32	4.50	12.82	1.64
XYC-206	324.2	327.3	3.1	7.42	1.65	9.09	2.86
Incl.	324.8	326.1	1.3	10.89	2.24	13.13	1.20
	346.1	347.4	1.3	6.14	3.71	9.85	1.20
	357.2	399.7	42.5	6.63	3.81	10.44	39.20
Incl.	358.1	361.2	3.1	7.80	2.98	10.78	2.86
Incl.	377.7	399.7	22.0	9.57	6.14	15.71	20.29
Incl.	384.3	391.0	6.7	16.64	12.27	28.91	6.18
Incl.	389.5	391.0	1.5	20.39	14.68	35.07	1.38
XYC-207	390.9	399.8	8.9	4.38	1.08	5.46	6.48
Incl.	391.7	394.6	2.9	7.69	1.49	9.18	2.11
	410.1	412.6	2.5	13.37	2.53	15.90	1.82
	416.7	417.1	0.4	9.27	1.62	10.89	0.30
XYC-208	482.1	507.4	25.3	6.47	4.61	11.08	23.19
Incl.	488.3	507.4	19.1	7.72	5.89	13.61	17.51
Incl.	501.6	507.4	5.8	15.78	16.89	32.67	5.32
Incl.	501.6	504.0	2.4	21.73	18.36	40.09	2.20
XYC-209	539.0	545.9	6.9	5.98	2.32	8.30	5.00
Incl.	541.6	545.9	4.3	7.44	3.20	10.64	3.11
Incl.	543.2	545.4	2.2	9.46	4.77	14.23	1.60
XYC-210	245.0	272.1	27.1	9.60	2.91	12.51	21.01
Incl.	254.0	256.0	2.0	12.22	2.65	14.87	1.55
Incl.	262.0	272.1	10.1	17.82	6.05	23.87	7.83
Incl.	263.2	269.9	6.7	21.13	7.58	28.71	5.19

Incl.	263.2	264.1	0.9	30.04	12.81	42.85	0.70
XYC-211	33.8	34.8	1.0	8.66	1.61	10.27	0.93
	135.6	140.7	5.1	6.65	1.79	8.44	4.75
XYC-212	214.3	217.6	3.3	5.50	1.71	7.21	0.20
XYC-213	206.5	208.8	2.3	5.79	1.68	7.47	1.18
Incl.	206.5	206.8	0.3	16.49	6.88	23.37	0.16
	212.2	212.7	0.5	11.11	1.82	12.93	0.26
	215.6	219.9	4.3	5.51	1.43	6.94	2.20
XYC-216	86.0	97.9	11.9	7.91	2.84	10.75	10.79
Incl.	86.0	88.9	2.9	15.30	3.62	18.92	2.63
Incl.	96.2	97.9	1.7	14.11	9.87	23.98	1.54
	102.9	103.7	0.8	13.33	11.82	25.15	0.73
	131.7	138.5	6.8	6.19	1.60	7.79	6.17
	143.4	148.8	5.4	6.64	1.82	8.46	4.90
Incl.	146.9	148.8	1.9	9.13	2.46	11.59	1.72
XYC-217	63.9	72.4	8.5	6.27	3.87	10.14	6.62
	63.9	66.4	2.5	10.27	3.12	13.39	1.95
XYC-218	119.0	125.5	6.5	10.42	1.81	12.23	5.00
XYC-219	310.8	327.2	16.4	9.23	4.18	13.41	9.56
Incl.	314.9	319.2	4.3	8.72	3.48	12.20	2.51
Incl.	323.6	327.2	3.6	21.84	11.85	33.69	2.10
XYC-221	148.5	155.7	7.2	19.23	17.74	36.98	6.65
Incl.	149.7	154.0	4.3	24.80	23.67	48.47	3.97
XYC-222	29.6	30.6	1.0	13.23	1.00	14.23	0.97
	83.6	89.4	5.8	9.60	1.59	11.19	5.62
Incl.	85.0	86.7	1.7	16.51	2.11	18.63	1.64
	103.6	114.1	10.5	16.05	4.71	20.76	10.16
Incl.	106.4	112.5	6.1	19.22	5.94	25.16	5.91
XYC-224	163.5	167.5	4.0	2.94	10.13	13.07	-
Incl.	164.1	166.0	1.9	4.76	15.18	19.93	-
	170.9	177.9	7.0	1.08	4.77	5.85	-
Incl.	175.7	177.9	2.2	1.92	7.89	9.81	-
XYC-226	97.1	113.7	16.6	6.45	1.78	8.23	14.95
Incl.	97.1	99.3	2.2	6.57	1.21	7.78	1.98
Incl.	103.3	104.2	0.9	13.06	3.27	16.32	0.81
Incl.	107.8	113.7	5.9	11.57	3.34	14.91	5.31
Incl.	109.6	111.4	1.8	28.12	7.07	35.19	1.62
XYC-227	Hole abandoned early						
XYC-228	186.2	198.8	12.6	4.15	2.62	6.77	10.80
XYC-229	Nil - ACTM faulted out						
XYC-230	70.4	81.1	10.7	6.77	2.13	8.90	9.88
Incl.	79.2	81.1	1.9	17.61	8.05	25.66	1.76
	124.0	141.5	17.5	9.51	3.25	12.76	16.17
Incl.	126.5	130.2	3.7	18.48	8.29	26.77	3.42
Incl.	137.7	141.5	3.8	14.57	2.89	17.46	3.51
Incl.	137.7	138.5	0.8	21.46	2.89	24.35	0.74
Incl.	140.3	141.5	1.2	26.21	5.56	31.77	1.11
XYC-231	ACTM was mostly barren						
XYC-232	45.0	47.6	2.6	7.77	1.17	8.94	2.60
Incl.	80.8	89.0	8.2	6.19	1.58	7.77	8.20
Incl.	80.8	83.2	2.4	8.81	1.65	10.46	2.40
	125.0	135.2	10.2	4.15	1.01	5.16	10.20
XYC-234	127.4	144.8	17.4	5.18	1.59	6.77	16.19
Incl.	127.4	129.7	2.3	11.30	2.85	14.15	2.14
Incl.	134.3	134.8	0.5	22.30	3.57	25.87	0.47

Incl.	138.3	144.8	6.5	6.14	1.75	7.89	6.05
XYC-235	69.2	98.3	29.1	5.43	1.67	7.10	29.10
Incl.	78.3	89.4	11.1	7.73	2.43	10.16	11.10
Incl.	81.8	87.9	6.1	10.89	3.26	14.15	6.10
Incl.	86.0	87.9	1.9	21.27	6.73	28.00	1.90
	121.6	139.8	18.2	5.54	1.12	6.66	18.20
Incl.	121.6	124.4	2.8	8.41	1.66	10.07	2.80
Incl.	129.0	137.0	8.0	8.03	1.50	9.53	8.00
Incl.	133.6	137.0	3.4	14.07	2.55	16.62	3.40
XYC-236	73.5	77.4	3.9	5.62	1.31	6.93	3.84
	80.6	82.2	1.6	5.16	0.62	5.78	1.57
	92.9	96.1	3.2	6.66	1.74	8.40	3.14
XYC-238	Nil - Drill hole collared in FW rock						
XYC-239	125.3	141.1	15.8	10.79	3.35	14.14	15.38
Incl.	133.4	141.1	7.7	17.17	5.30	22.47	7.50
Incl.	136.1	141.1	5.0	22.86	7.19	30.05	4.87
XYC-240	15.6	16.2	0.6	7.94	1.00	8.94	0.60
	62.4	63.7	1.3	10.66	2.49	13.15	1.30
	72.1	77.2	5.1	6.39	2.25	8.64	5.10
	116.0	134.0	18.0	5.55	1.20	6.75	17.59
Incl.	116.0	120.9	4.9	10.98	2.13	13.11	4.79
Incl.	116.9	118.4	1.5	23.49	3.06	26.55	1.46
Incl.	131.3	132.9	1.6	9.25	1.24	10.49	1.56
XYC-241	479.3	481.4	2.1	5.86	0.70	6.56	1.80
	487.5	488.2	0.7	13.84	2.06	15.90	0.60
	493.5	503.6	10.1	6.62	1.87	8.49	8.67
Incl.	498.8	503.6	4.8	9.90	2.66	12.56	4.12
Incl.	499.8	502.6	2.8	12.37	3.26	15.63	2.40
	513.0	513.3	0.3	6.53	5.66	12.19	0.26

Table 5: Mineralized intercepts in XY Central deposit drill holes filed for assessment.

3.2.2. XY West Deposit

DDH XYC-214: Exploration drilling in the XY West deposit. Drill hole depth is 248.5m with NQ core size. The drill hole collared in Backside Siliceous Mudstone which was intersected to a depth of 49.1m; it intersected Flaggy Mudstone from 49.1m to 168.0m, Upper Siliceous Mudstone from 168.0m to 218.3m, a fault from 218.3m to 221.9m, Flaggy Mudstone from 221.9m to 227.4m, Upper Siliceous Mudstone from 227.4m to 248.5m; EOH.

DDH XYC-215: Exploration drilling in the XY West deposit. Drill hole depth is 432.2m with NQ core size. The drill hole collared in Backside Siliceous Mudstone which was intersected to a depth of 8.6m; it intersected a fault from 8.6m to 22.5m, Flaggy Mudstone from 22.5m to 164.2m, Upper Siliceous Mudstone from 164.2m to 317.3m, Active Member from 317.3m to 340.5m, Calcareous Mudstone from 340.5m to 345.5m, a fault from 345.5m to 357.6m, Upper Siliceous Mudstone from 357.6m to 371.0m, Active Member from 371.0m to 390.9m, Calcareous Mudstone from 390.9m to 432.2m; EOH.

DDH XYC-220: Exploration drilling in the XY West deposit. Drill hole depth is 281.5m with NQ core size. The drill hole collared in Flaggy Mudstone which was

intersected to a depth of 140.9m; it intersected a fault from 140.9m to 181.7m, Active Member from 181.7m to 252.4m, a fault from 252.4m to 267.3, Backside Siliceous Mudstone from 267.3m to 281.5m; EOH.

DDH XYC-223: Exploration drilling in the XY West deposit. Drill hole depth is 648.4m with NQ core size. The drill hole collared in a fault which was intersected to a depth of 46.0m; it intersected Active Member from 46.0m to 111.8m, Upper Siliceous Mudstone from 111.8m to 182.2m, Active Member from 182.2m to 252.5m, a fault from 252.5m to 260.1m, Upper Siliceous Mudstone from 260.1m to 275.2m, Active Member from 275.2m to 337.5m, a fault from 337.5m to 341.4m, Calcareous Mudstone from 341.4m to 398.0m, a fault from 398.0m to 419.4m, Flaggy Mudstone from 419.4m to 581.1m, Upper Siliceous Mudstone from 581.1m to 615.9m, Active Member from 615.9m to 627.5m, Calcareous Mudstone from 627.5m to 648.4m; EOH.

DDH XYC-225: Exploration drilling in the XY West deposit. Drill hole depth is 654.4m with NQ/BQ core size. The drill hole collared in Flaggy Mudstone which was intersected to a depth of 343.8m; it intersected Upper Siliceous Mudstone from 343.8m to 475.4m, Active Member from 475.4m to 537.5m, Calcareous Mudstone from 537.5m to 538.8m, a fault from 538.8m to 555.8m, Backside Siliceous Mudstone from 555.8m to 654.4m; EOH.

DDH XYC-233: Exploration drilling in the XY West deposit. Drill hole depth is 719.0m with NQ/BQ core size. The drill hole collared in a fault which was intersected to a depth of 36.9m; it intersected Active Member from 36.9m to 254.1m, a fault from 254.1m to 258.4m, Upper Siliceous Mudstone from 258.4m to 336.8m, Active Member from 336.8m to 357.6m, a fault from 357.6m to 382.8m, Calcareous Mudstone from 382.8m to 536.3m, a fault from 536.3m to 578.5m, Flaggy Mudstone from 578.5m to 630.1m, Upper Siliceous Mudstone from 630.1m to 663.0m, Active Member from 663.0m to 695.2m, Calcareous Mudstone from 695.2m to 719.0m; EOH.

DDH XYC-237: Exploration drilling in the XY West deposit. Drill hole depth is 404.3m with NQ core size. The drill hole collared in Flaggy Mudstone which was intersected to a depth of 33.0m; it intersected Upper Siliceous Mudstone from 33.0m to 104.0m, a fault from 104.0m to 133.8m, Flaggy Mudstone from 133.8m to 161.8m, Upper Siliceous Mudstone from 161.8m to 213.0m, Active Member from 213.0m to 235.0m, a fault from 235.0m to 238.8m, Calcareous Mudstone from 238.8m to 377.8m, Transition Formation from 377.8m to 404.3m; EOH.

DDH#	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Pb+Zn (%)	True Width (m)
XYC-214	Nil - No ACTM at target depth because of fault, hole abandoned in HW rock below fault						
XYC-215	Assays have not been released yet						
XYC-220	Assays have not been released yet						
XYC-223	Assays have not been released yet						
XYC-225	Assays have not been released yet						
XYC-233	Assays have not been released yet						
XYC-237	Assays have not been released yet						

Table 6: Mineralized intercepts in XY West deposit drill holes filed for assessment.

3.3. Sample Preparation, Analysis and Security

3.3.1. Analytical Procedures

As of June 14, 2011, exactly 2,514 core samples from drill holes XYC-190 to XYC-241 were shipped to ACME Analytical Laboratories Ltd. (“ACME”), 77 Collins Lane, Whitehorse, Yukon Territory, Y1A 0A8. Note that the core samples of drill holes XYC-223, XYC-233 and XYC-237 have not been shipped to Whitehorse yet. Also note that XYC-199 was re-sampled.

Upon reaching ACME’s preparation lab in Whitehorse, the samples were logged into an internal tracking system and the sample weight was recorded. Each sample was then dried and crushed to 80% passing 10 mesh (1.6 mm). A 250 gram split was then pulverized to 85% passing 200 mesh (74 µm) in a mild-steel ring-and-puck mill. That split was then sent to ACME’s analytical lab, 1020 East Cordova Street, Vancouver, British Columbia, V6A 4A3. Each core sample was reduced to a 0.5 gram light sample that underwent multi-acid (HCl, HF, HNO₃, HClO₄) digestion and was analyzed with an ICP-ES for a suite of 23 elements. Specific gravity analyses were undertaken for each sample. Raw and final data from the ICP-ES undergoes a final verification by a British Columbia Certified Assayer who then signs the Analytical Report before it is released to the client.

Geochemical results are included in Appendix E.

3.3.2. Security and Chain of Custody

All core samples were shipped off to Whitehorse from Don Camp in well secured rice bags; which were closed with metal tie straps to prevent tampering. From camp, the samples were delivered to Whitehorse via Alkan Air fixed-wing aircrafts, where the secured rice bags were unloaded in the locked compound and possibly stored for a short time. At Alkan Air, the secured rice bags were picked up by an ACME employee and transported to ACME’s preparation lab in Whitehorse for sample preparation. The prepared samples were then flown to Vancouver for analysis in ACME’s analytical lab. All samples were tracked throughout this process; noting that both fax and e-mail notice was provided to Selwyn at each step during the delivery process. When the Whitehorse laboratory received samples, final official notification to Selwyn was provided; which signaled the commencement of sample preparation and analytical work. It should be noted that Selwyn’s standing policy is that the Company is notified immediately if there are any broken straps within the secure rice bag shipment.

3.3.3. QA/QC Program

Selwyn has a well established comprehensive sampling and assay control program that includes the blind insertion of assay duplicates, blanks and standards; which are in addition to the detailed quality control and quality assurance programs of ACME; which were also made available to Selwyn.

All drill core samples were divided into groups of 30 samples for QA/QC purposes. Each group of 30 samples contained one duplicate sample, one blank sample and one industrial geochemical standard sample; placed on the 11th, 20th and 30th location respectively within the sequence of 30 samples. The original sample for the duplicate sample was on the 10th location within the sequence of 30 samples. Duplicate samples were taken by cutting the original half-core sample into two quarter-core samples. Blank samples consisted of crushed marble. Industrial geochemical standard samples were provided by the commercial supplier WCM Minerals (WCM Sales Ltd, 7729 Patterson Ave, Burnaby, British Columbia). Note that at least one standard, one blank and one duplicate is inserted per drill hole submitted for assay analysis. A short summary on the QAQC samples submitted with the core samples of the drill holes filed for assessment are described below.

Standards

Both lead/zinc standards A and B, which were used in every drill program from 2005 to 2009, were used for a brief period in 2010's drill program until we ran out of them. Standard C and D are now the new lead/zinc standards. A total of seventy three (73) standard samples (11 Std A, 13 Std B, 29 Std C & 20 Std D) were submitted for analysis together with the drill core samples. Standard A has following certified grades: 1.27% zinc, 0.92% lead, 0.85% copper and 222g/t silver. Standard B has 4.16% zinc, 1.47% lead, 0.50% copper and 30g/t silver. Standard C has 6.88% zinc, 6.06% lead, 0.68% copper and 70g/t silver. Standard D has 2.87% zinc, 1.43% lead, 0.48% copper and 19g/t silver.

All Standards A passed QAQC standards and are within a +/-2 standard deviation, except for one sample which had slightly less Pb, but still within acceptable limits. All Standards B passed QAQC standards and are within a +/-2 standard deviation, except for one sample which had slightly less Cu, but still within acceptable limits. All Standards C passed QAQC standards and are within a +/-2 standard deviation, except for one sample which had slightly less Ag & Zn and one other sample which had slightly more Cu. Both anomalies are still within acceptable limits. All Standards D passed QAQC standards and are within a +/-2 standard deviation, except for one sample which had slightly less Cu and one other sample which had slightly less Zn. Both anomalies are still within acceptable limits.

Blanks

A total of eighty (80) blanks were submitted for analysis together with the drill core samples. All blanks passed QAQC standards and plotted within +/- 2 standard deviation. Ca and Mg showed normal values. No Zn or Pb was detected in most blanks, except for 4 samples which showed only minor contamination:

- Sample # 632730 (XYC-206): 0.12 % Pb and 0.11 % Zn
- Sample # 635350 (XYC-230): 0.05 % Pb and 0.12 % Zn
- Sample # 632110 (XYC-190): 0.05 % Pb
- Sample # 635120 (XYC-239): 0.07 % Zn

Duplicates

A total of ninety one (91) duplicate samples were submitted for analysis together with the drill core samples. The majority of the duplicates are within a +/-30% tolerance. The original/duplicates tend to be within the limits towards the higher values, as they should be. The element Pb shows slightly more anomalies than Zn, which can very probably be explained by the occurrence of galena blebs in the core. Correlation plots (X-Y) were constructed for zinc, lead, silver, aluminum, calcium and iron with a regression line: $f(x) = y$ and two tolerance lines at +/-30% of the regression line. No major concerns were identified.

Internal Quality Control at ACME Laboratories

At ACME laboratories, internal QA/QC reports were sent to Selwyn along with the original data from each geochemical submission to the laboratory. These QA/QC reports included data from the analysis of certified and in-house standards, blanks, and duplicates done in order to maintain quality control for the laboratory. The recording technician and the Chief Technician verified all results prior to data being sent to Selwyn.

4. Summary and Recommendations

In 2010, Selwyn focused its drilling activities on three areas: XY Central deposit definition drilling, XY West deposit exploration drilling, and Don deposit definition and exploration drilling.

XY Central Deposit Definition Drilling

A drilling program was designed to upgrade and prove the resources at XY Central in order to fulfill the request for the Bankable Feasibility Study 1. All the results were given to third party Qualified Persons for auditing in compliance with NI 43-101. No data is available at this point in time.

XY West Deposit Exploration Drilling

It was previously recognized that the XY West deposit had seen limited exploration and could host additional high grade resources. By the end of 2010, most holes intercepted mineralized Active Member. The current interpretation suggests that 1) the XY Central and XY West deposits belong to separate thrust blocks and 2) the extension of ore lenses at the XY west would trend toward west and dip to north with a possible repetition. Follow up drilling is recommended in order to define more resources.

5.0. References

<http://www.mapsyukon.gov.yk.ca>

<http://www.selwynresources.com/>

Burgoyne, A.A. 2005: Technical Evaluation Report for Pacifica Resources Ltd. on the Howard's Pass Project, Yukon-Northwest Territory Border, Canada. Burgoyne Geological Inc., 69p.

Cousens, B.L. 2006: Radiogenic isotope studies of Pb-Zn mineralization in the Howard's pass area, Selwyn Basin. *In* H. Falck and D.F. Wright, eds., Mineral and Energy Resources Potential of the Proposed Expansion to the Nahanni National Park Reserve, North Cordillera, Northwest Territories; Geological Survey of Canada, Open file 5344.

De Bruyckere, J. 2010: Howard's Pass Internal Report 2009

Deklerk, R. and Traynor, S. (compilers) 2005: Yukon MINFILE 2005 – A database of mineral occurrences. Yukon Geological Survey. CD-ROM.

Goodfellow, W.D. 2006: Metallogeny of the Selwyn Basin, Canada, *in* W.D. Goodfellow, ed., Mineral Deposits of Canada: A Synthesis of Major Deposit Types, District Metallogeny, the Evolution of Geological Provinces, and Exploration Methods: Geological Association of Canada, Mineral Deposits Division, Special Publication.

Goodfellow, W.D. 2004: Geology, genesis and exploration of SEDEX deposits, with emphasis on the Selwyn Basin, Canada. *In* Deb, M. and Goodfellow, W. eds., Sedimenthosted Lead-Zinc Sulphide Deposits: Attributes and Models of Some Major Deposits of India, Australia and Canada: Delhi, India, Narosa Publishing House, pp24-99.

Goodfellow, W.D. and Jonasson, I.R. 1987: Environment of formation of the Howard's Pass (XY) Zn-Pb deposit, Selwyn Basin, Yukon. *In* Morin, J.A. ed., Canadian Institute of Mining and Metallurgy Special Volume 37, pp19-50.

Gordey, S.P. and Anderson, R.G. 1993: Evolution of the Northern Cordilleran Miogeocline, Nahanni Map Area (105I), Yukon and Northwest Territories. Geological Survey of Canada Memoir 428, 214p.

Hodder, R.W. and Bain, D.J. 2010: Howard's Pass: Interpretation of Thrust Faults From Field Observations in 2010.

Morganti, J.M. 1979: The Geology and Ore Deposits of the Howard's Pass Area, Yukon and Northwest Territories: The Origin of Basinal Sedimentary Stratiform Sulphide Deposits; PhD thesis, 327p.

Morganti, J.M. 1982: Howard's Pass Evaluation/Summary Report, Placer Development Ltd.

Pearson, C. and O'Donnell, J. 2008: Update Resource Estimate Report for the Selwyn Project Yukon-NWT, Canada, 135p.

APPENDICES

Appendix A
Statement of Expenditures


STATEMENT OF EXPENDITURES

I, Michael Mayer, as agent for Selwyn Chihong Mining Ltd, #700-509 Richards Street, Vancouver, B.C. do solemnly declare that drilling carried out on the Howard's Pass Claims (see attached list) between the dates of June 14th, 2010 and October 31st, 2010.


Drilling	
Drilling Cost	\$2,874,761.14
Total	\$2,874,761.14

I make this solemn declaration conscientiously believing it to be true and knowing that it is of the same force and effect as if made under oath and by virtue of the Canada Evidence Act.

Declared before me at Vancouver in the Province of British Columbia this 17th day of December 2010 ~~2009~~



Michael Mayer



Notary Public

Lance Bredeson
BARRISTER AND SOLICITOR
LANG MICHENER LLP
1500-1055 WEST GEORGIA STREET
P.O. BOX 11117
VANCOUVER, B.C. V6E 4N7
TELEPHONE: 604 689-9111

Appendix B
Statement of Qualifications



Suite 700 – 509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

Telephone: +1 (604) 801-7240
Toll-free: 1 (888)-989-7240

Fax: +1 (604) 689-8355
info@selwynresources.com
www.selwynresources.com

Statement of Qualifications


I, Jelle De Bruyckere, resident of Vancouver, British Columbia, do certify that:

1. I graduated from Ghent University in Belgium in September 2004 with a M.Sc. in Geology;
2. From July 2005 to present, I have been actively engaged in mineral exploration in Northwest Territories and Yukon Territory and I am presently employed with Selwyn Resources Ltd.;
3. I have personally participated in the fieldwork and analysis of data in the office for the filed undertakings herein.

Respectfully submitted,

A handwritten signature in black ink, appearing to read 'Jelle De Bruyckere', is written over a horizontal line.

Jelle De Bruyckere, M.Sc.

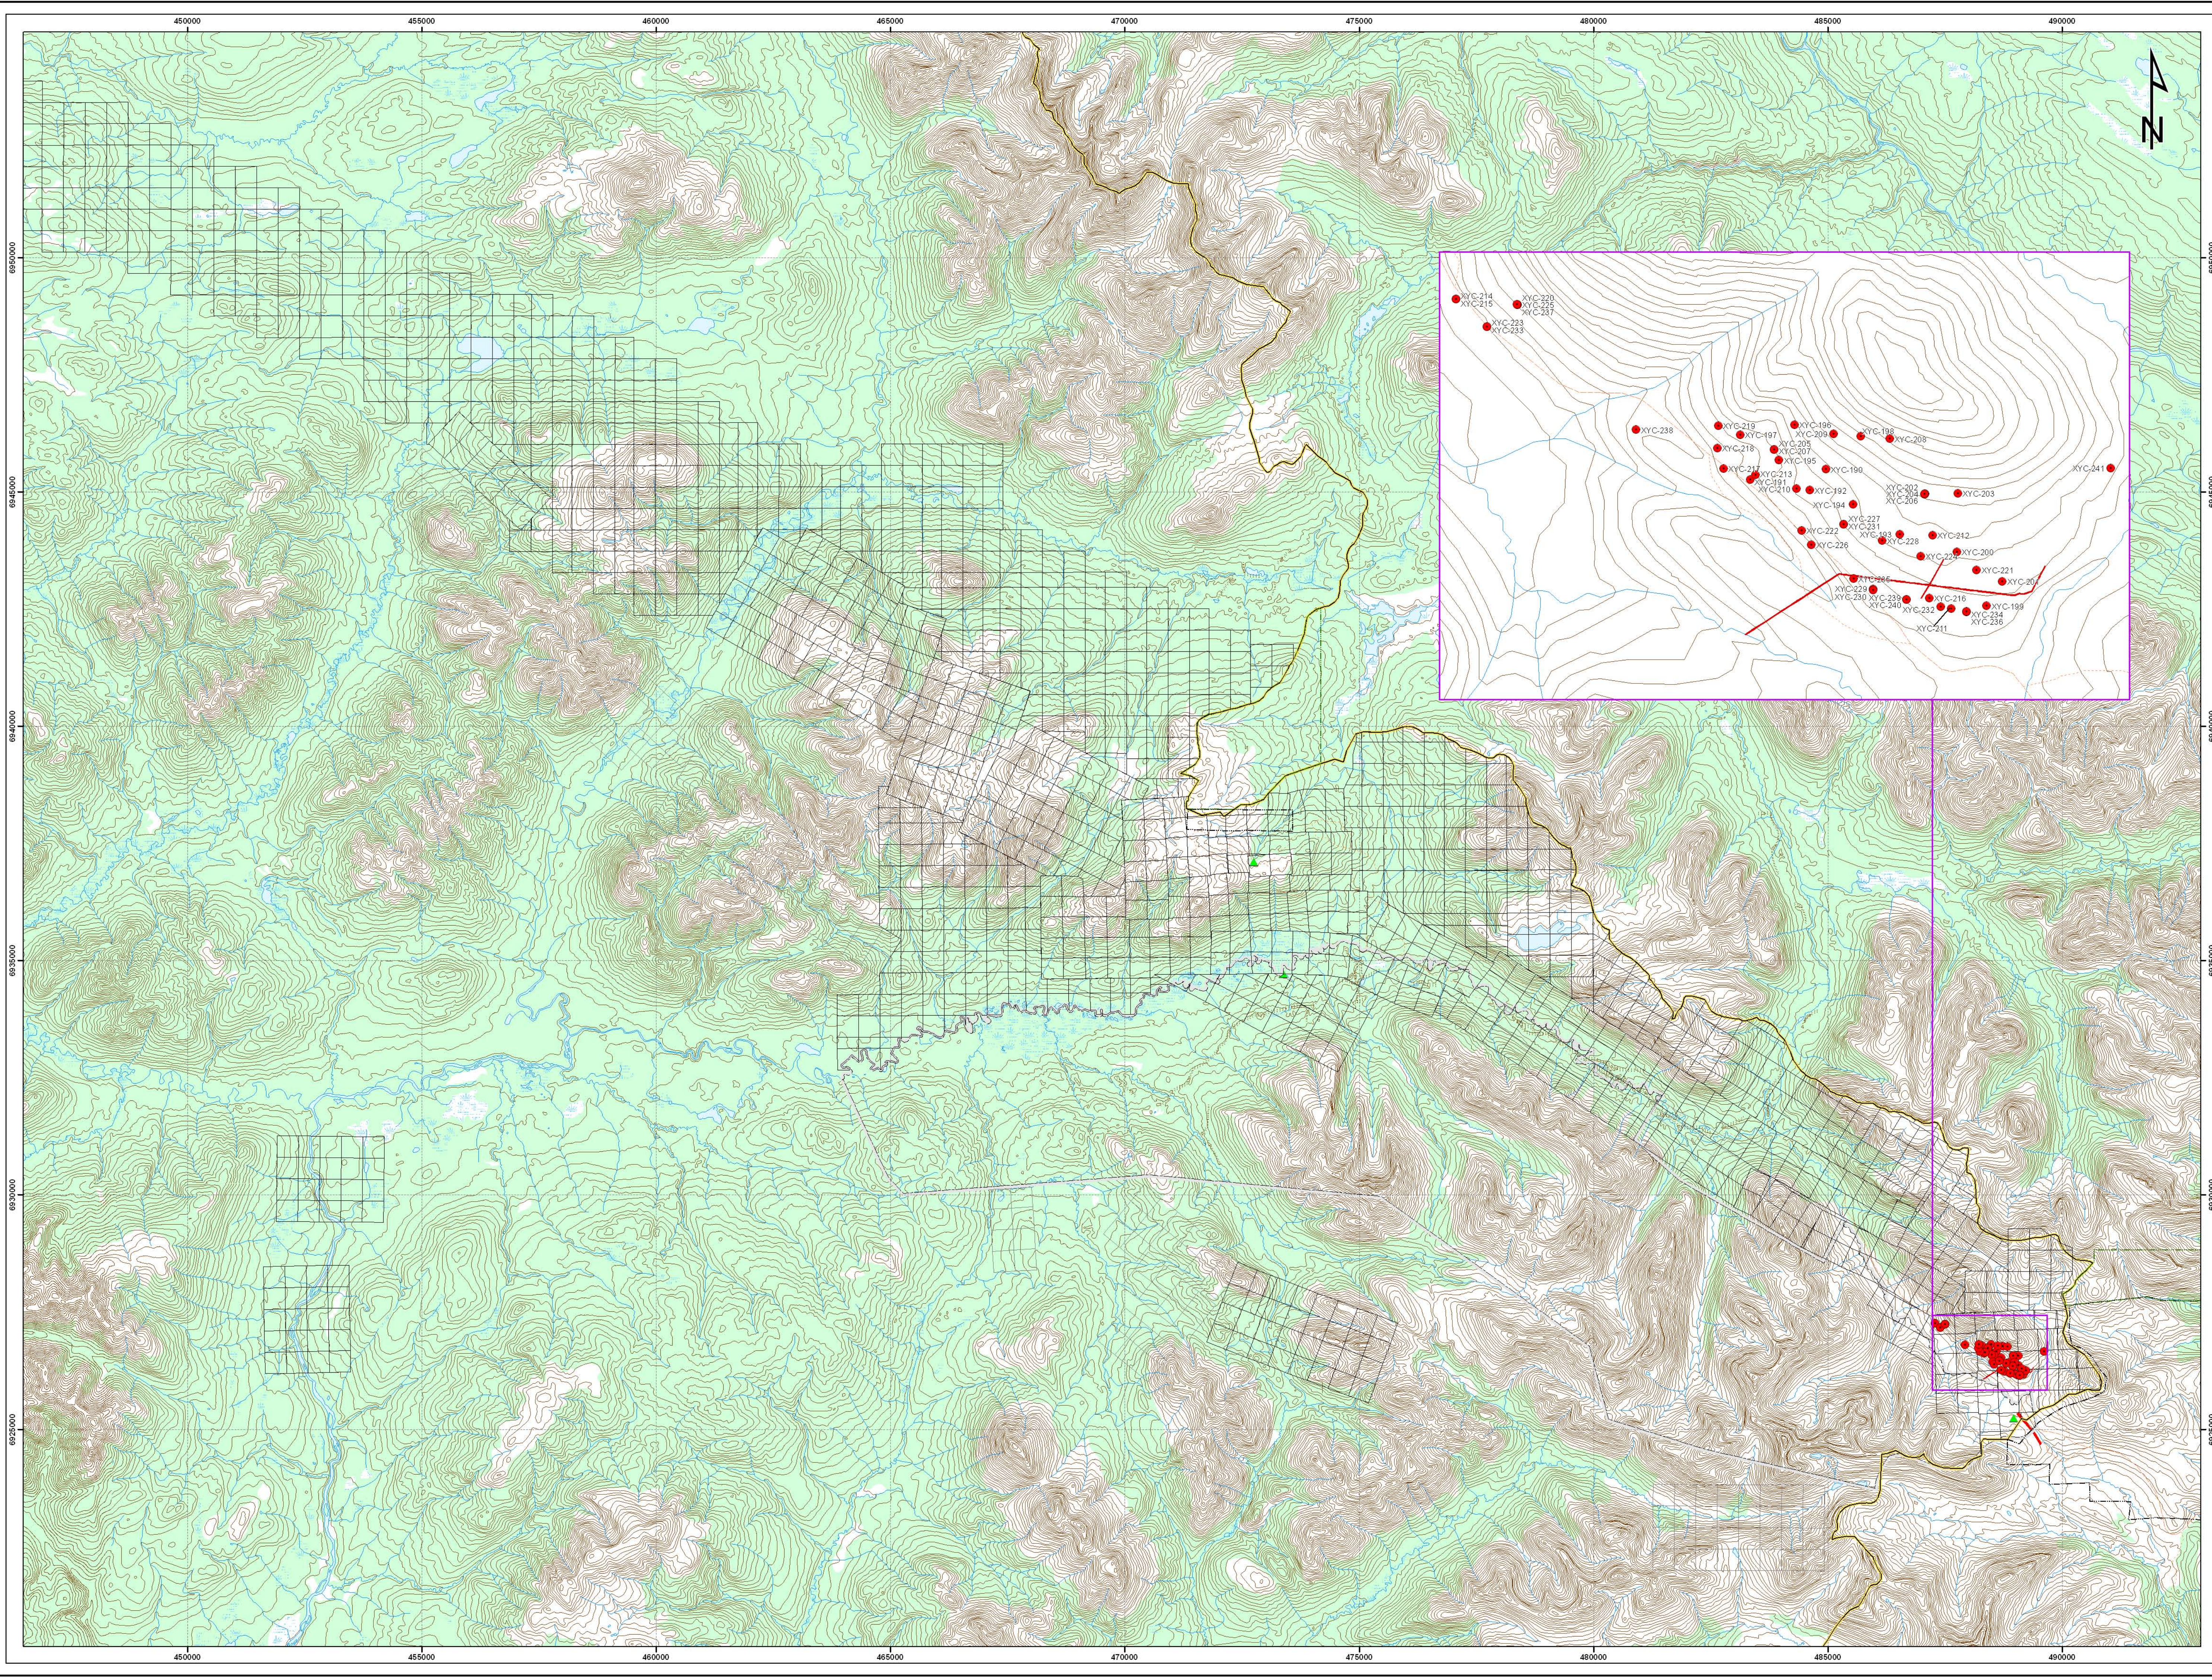

Alaska

Northwest Territories

Yukon

Map Area

Whitehorse

Watson Lake

Legend

Selwyn Chihong Collars

● 2010

Underground Drift

Boundaries

SCML Claims

NWT SCML

NWT Howard's Pass JV

Other Quartz Mineral Claims

Yukon & NWT Border

Interim Protected Lands

Topography

SCML Exploration Camp

Airstrip

Roads

Trails

Limited-Use Roads

Eskers

Moraines

Sand

Streams

Wetlands

Dry Streams

Lakes

Vegetation

Contours

Date: 2010/11/17

Author: M. Mayer

Office: Vancouver

Figure: 2

Scale: 1:60,000

Selwyn Project

2010 XYC & XYW

Drill Collars

Figure 2


Filename: SC1710_rept_20110620_2010AssessmentCollars.mxd

Project Location: Watson Lake Mining District - NTS 1051/J

Projection: NAD83 - UTM Zone 9

0 1 2 3 4

Kilometers

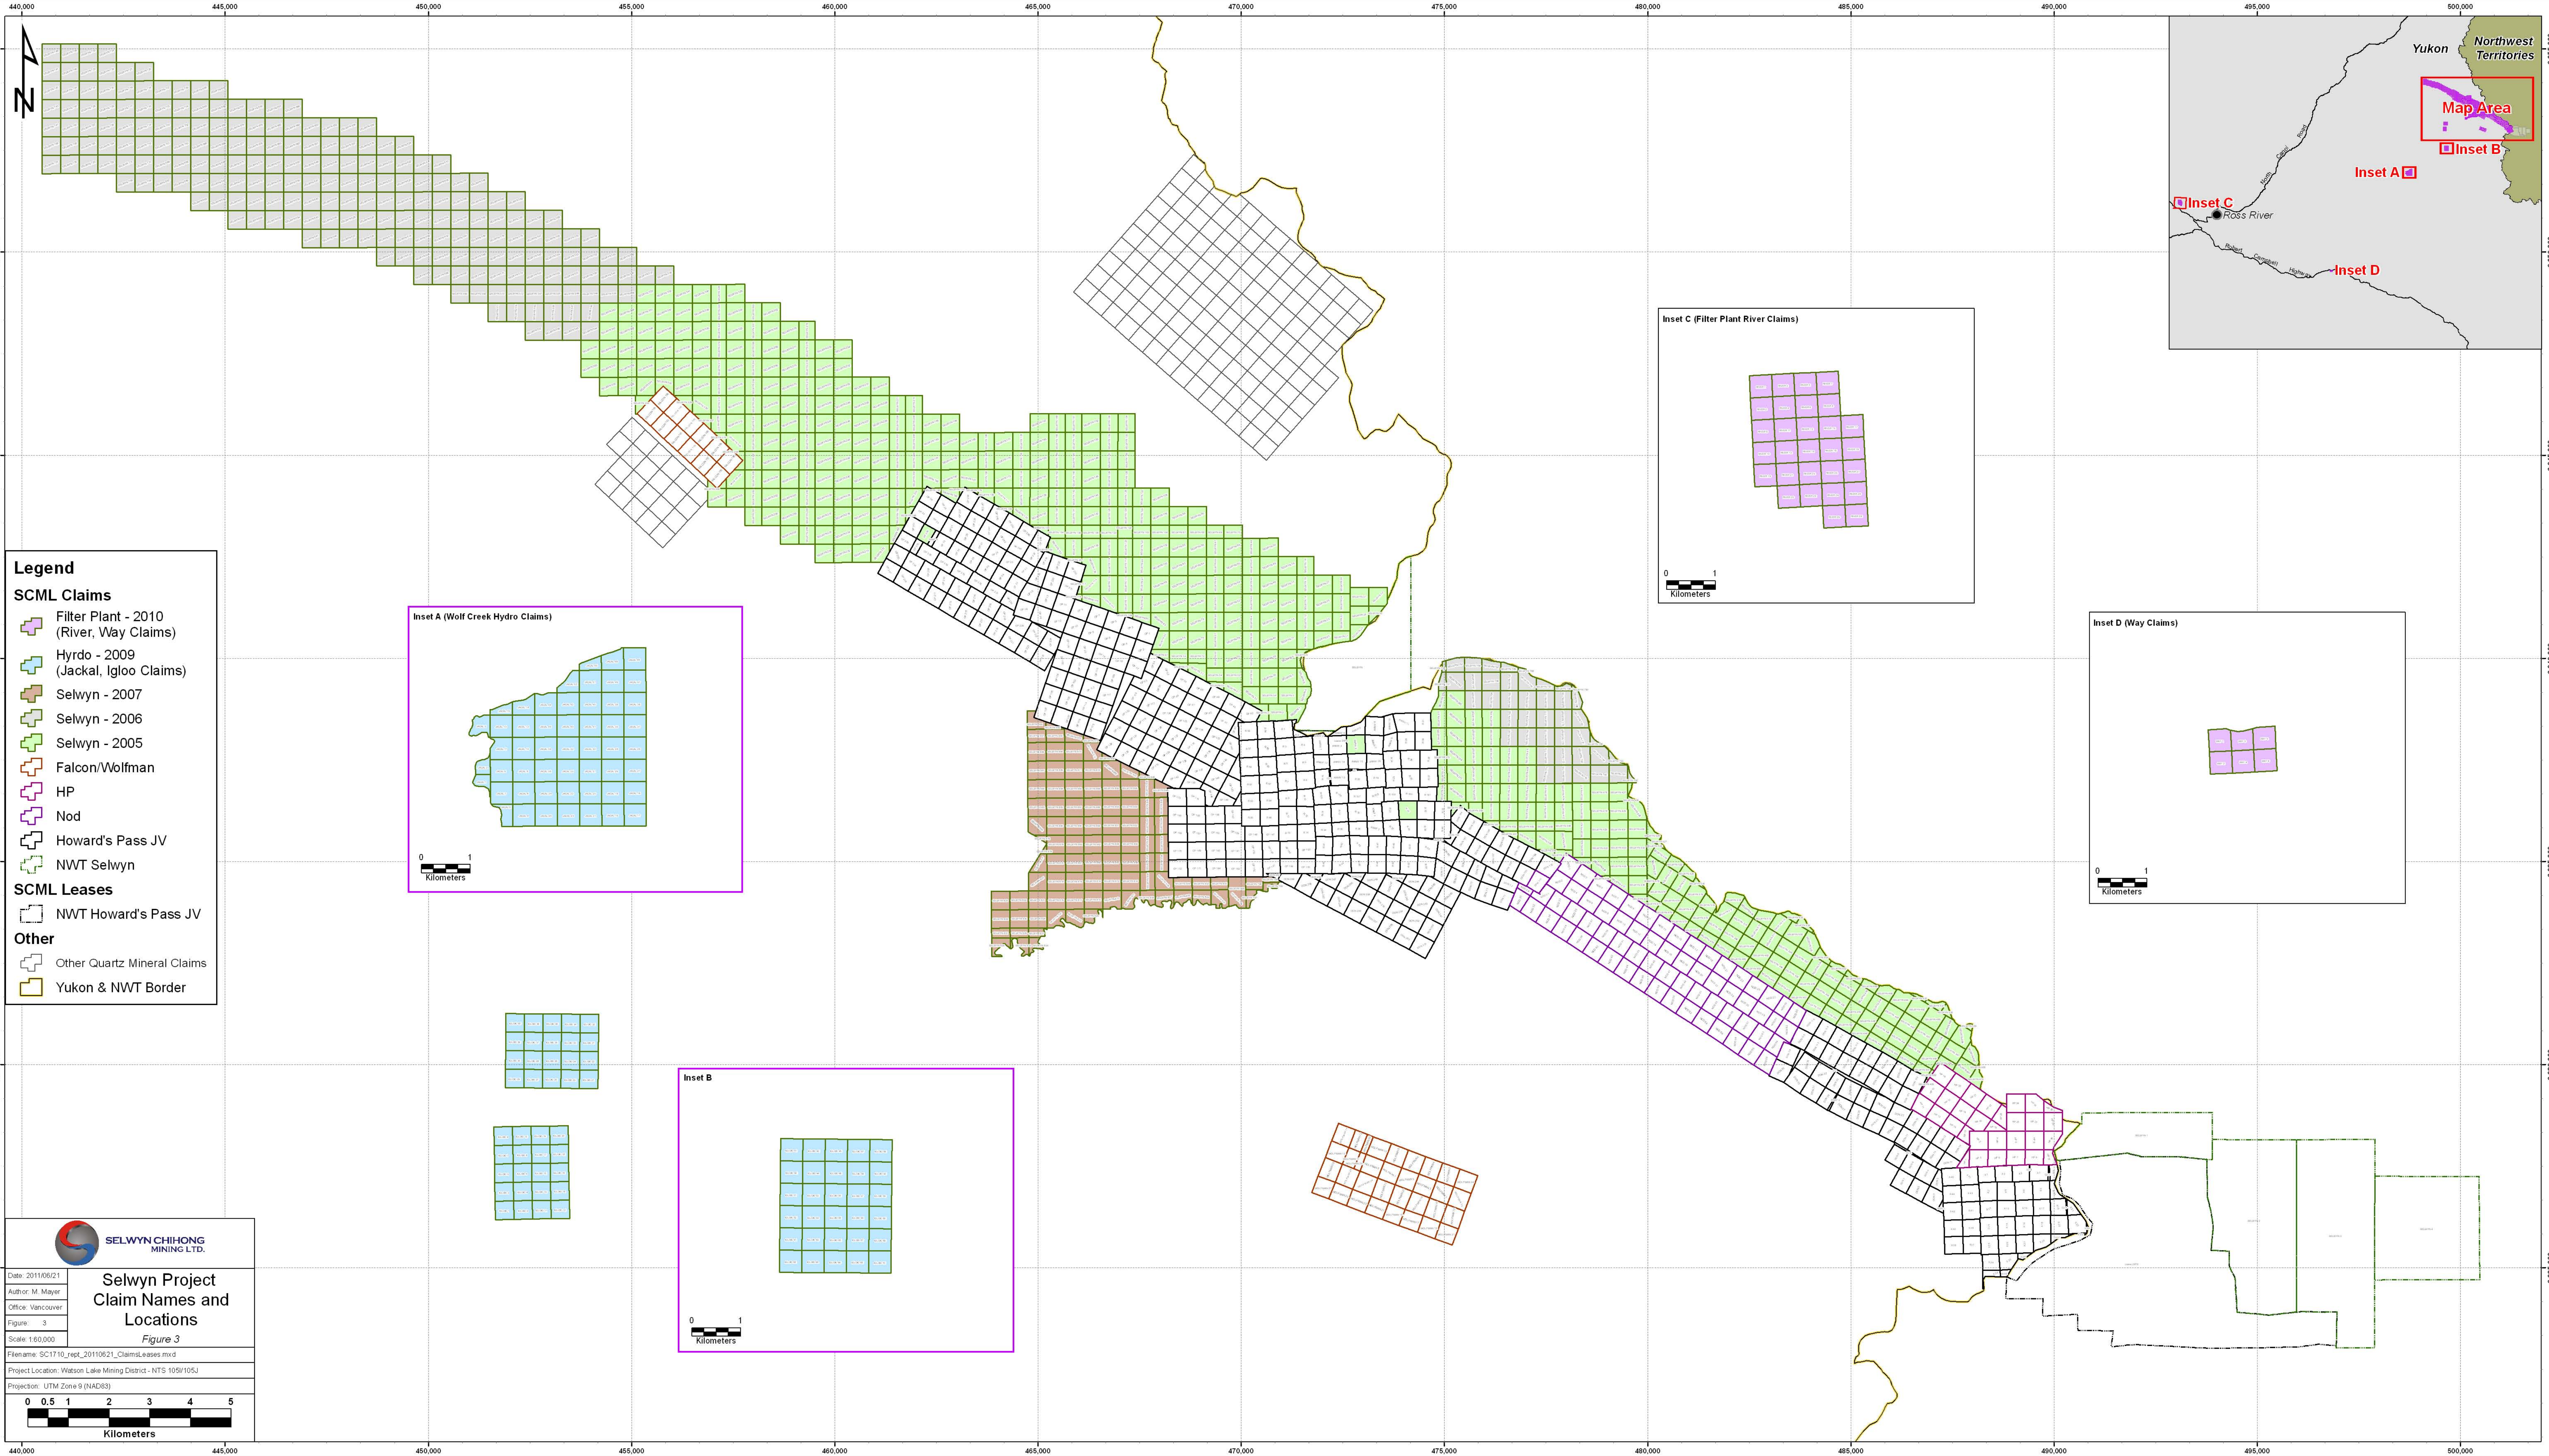

Legend

SCML Claims

Filter Plant - 2010
(River, Way Claims)

Hyrdo - 2009
(Jackal, Igloo Claims)

Selwyn - 2007

Selwyn - 2006

Selwyn - 2005

Falcon/Wolfman

HP

Nod

Howard's Pass JV

NWT Selwyn





SCML Leases

NWT Howard's Pass JV

Other

Other Quartz Mineral Claims

Yukon & NWT Border

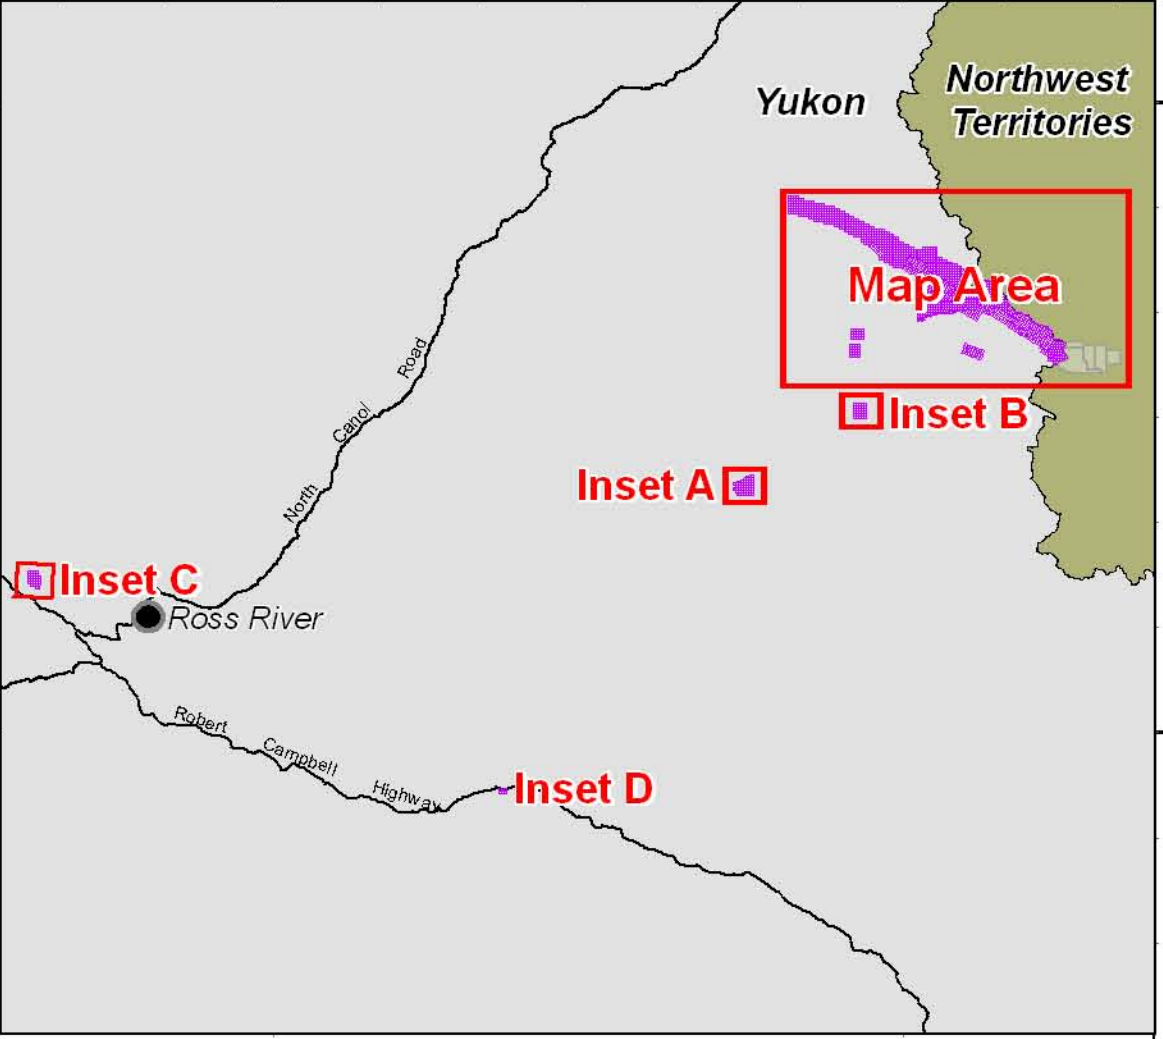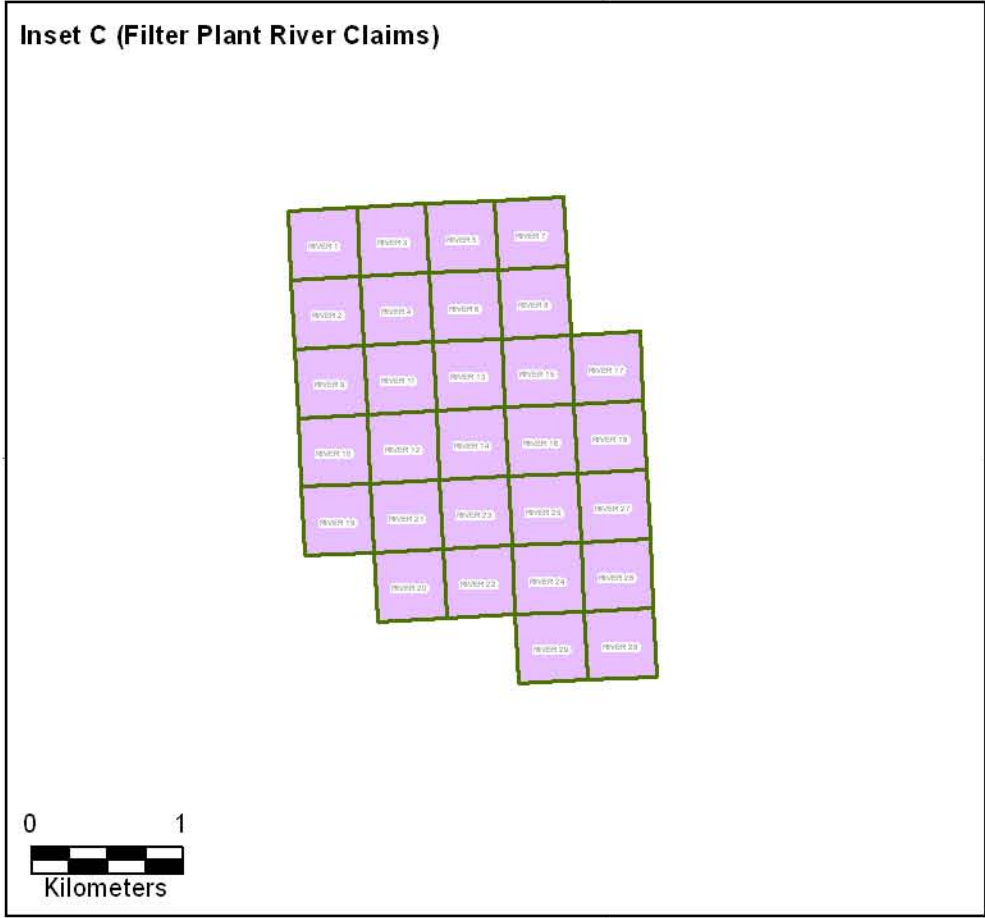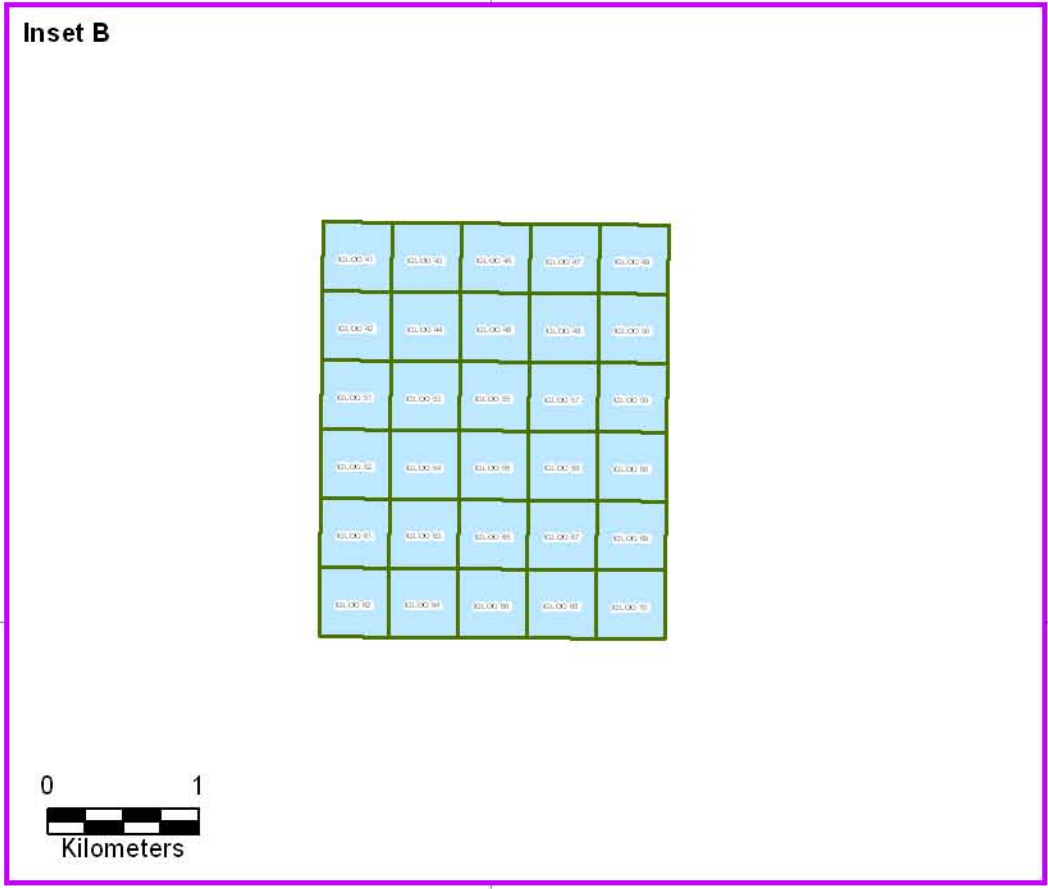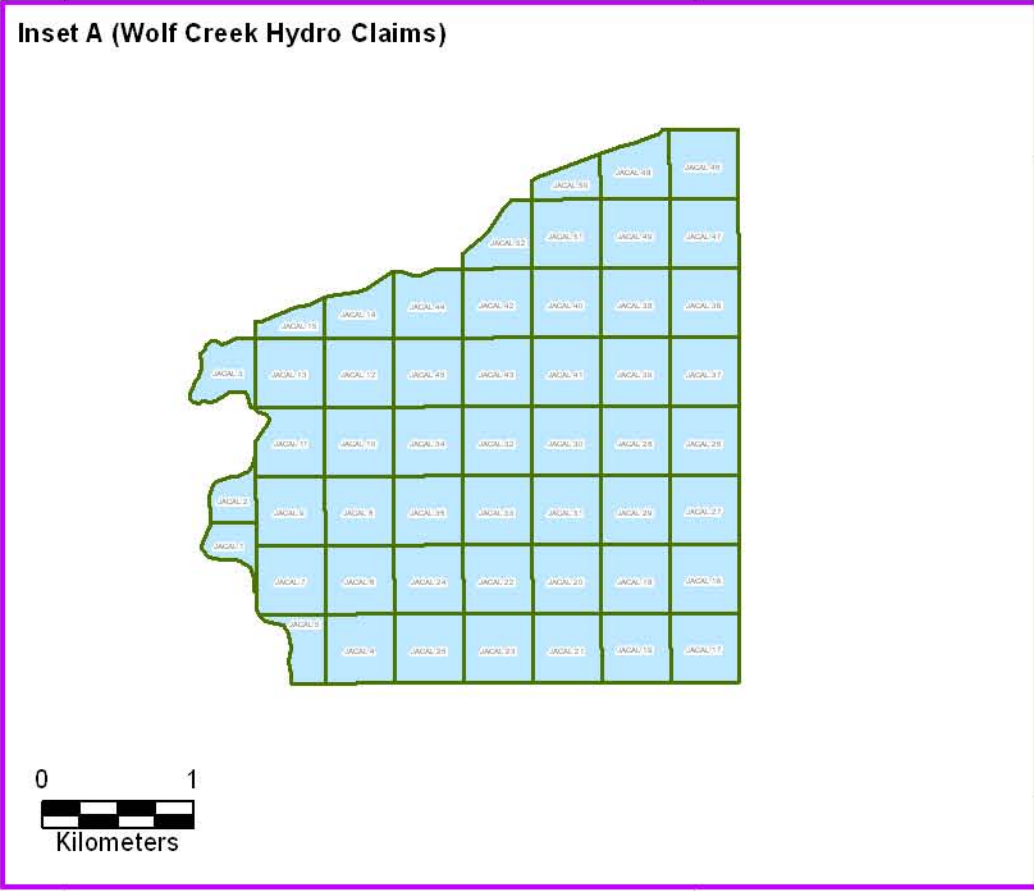

Date: 2011/06/21

Author: M. Mayer

Office: Vancouver

Figure: 3

Scale: 1:60,000

Selwyn Project

Claim Names and

Locations

Figure 3

Filename: SC1710_rept_20110621_ClaimsLeases.mxd

Project Location: Watson Lake Mining District - NTS 105/105J

Projection: UTM Zone 9 (NAD83)

Diamond Drill Log

Comprehensive Report for Hole:

XYC-241

Hole No.: XYC-241	Depth: 550.00 m	Horizontal Length: 0.00 m	Project: 1710
Location Data:			
Property:	Selwyn Project	Claim Name:	X17
Mining District:	Selwyn Basin	Grant Number:	Y 64542
Province/Territory:	Yukon		
UTM Co-Ordinates & Altitude of Drill Hole Collar:			
UTM Easting:	489614.00 m	True Azimuth:	180.0 °
UTM Northing:	6926660.00 m	Hole Angle:	-74.0 °
Elevation (m):	1628.00 m	NTS Name:	Placer Creek
		NTS Number:	105L06
Grid Co-Ordinates of Drill Hole Collar:			
Grid Easting (m):	0.00 m	Grid Name:	HP 06
Grid Northing (m):	0.00 m	Grid Type:	100m
Grid Azimuth:	240.0 °		
Dimond Drilling Contract:			
Drilled By:	CY-03	Date Drilling Start:	10/30/2010
		Date Finish:	11/8/2010
Diamond Drill Core:			
Logged By:	Kate Cameron	Date Logging Start:	01/7/2011
		Date Finish:	01/14/2011
Legend for Core Logging Codes: PAX			
Core Size:	NQ	Cemented:	Yes
Casing Depth:	10.80 m	Casing Pulled:	Yes
Water Depth:	0.00 m	Overburden Depth:	10.80 m
Level:			
Section:		Drift:	

Selwyn Project

Diamond Drill Log

Survey Data for Hole

XYC-241

Hole Comments:

Thu, Oct 28 --- Most of the drill components were moved to site yesterday. Will likely begin drilling tomorrow.

=====

Fri, Oct 29 --- Still mobilizing pump shack, hose line, and generator to the pad. Drilling will likely not start until tomorrow.

=====

Sat, Oct 30 --- Should start drilling today.

=====

Sun, Oct 31 --- The drill is now set up and ready to go after a few more minor delays. 9m of casing down. Will start coring this morning

=====

Mon, Nov 01 --- Total depth 93m. The unit is likely BSSM, with large zones of black massive mdst, and lighter grey chert banding locally with medium-coarse grained clasts or bedding, some of these showing grading.

=====

Tue, Nov 02 --- Total depth 159m. Core was examined in snowy, frozen conditions, but it appears to still be BSSM.

=====

Wed, Nov 03 --- Total depth 241m. Fault with 15% gouge, 50% broken core from 232m-241m. The rock type is looking more and more like CCMS, for the past 80m+ there have been no indicators of BSSM, just monotonous black mudstone with typical CCMS calcite and pyrite beds

=====

Thu, Nov 04 --- "321m deep, strongly fractured core from 262 to 309m, likely in BSSM. No problems to report."

=====

Fri, Nov 05 --- "Steady drilling at 399 meters in BSSM, with bioturbations observed from 369."

=====

Sat, Nov 06 --- At 450 meters; pulled rod to change the bit. Unsure of geology as the core was not able to be examined yet due to lack of vehicles. Will update geology tomorrow. Drill was shut down for 2 hours last night due to severe drifting snow.

=====

Sun, Nov 07 --- "In ACTM @507m, tentative contact @ 486m. "

=====

Mon, Nov 08 --- "In CCMS at 537m, ACTM/CCMS at 514m. Will shut down at 552m and cement, moving to Don Zone after the CY-01 move is complete. Will likely set up on d5 there, which is a deep, priority hole."

<i>Depth</i>	<i>Dip</i>	<i>Azimuth</i>
0.00	-74.0	180.0
50.00	-73.7	182.7
102.00	-74.0	184.0
150.00	-72.5	181.8

Selwyn Project

Diamond Drill Log

Survey Data for Hole

XYC-241

Selwyn Chihong Mining Ltd.#700-509 Richards Street
Vancouver, British Columbia
Canada V6B 2Z6

201.00	-72.0	183.6
252.00	-72.2	186.1
300.00	-71.7	186.1
350.00	-72.0	188.6
402.00	-71.2	190.2
450.00	-70.4	190.9
501.00	-69.9	190.2
550.00	-69.2	192.0

Selwyn Project Diamond Drill Log

Hole Number:
XYC-241

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
0.00	10.80	OVBR									
10.80	309.00	BSSM									
<i>BSSM – Backside Siliceous Mudstone</i> <i>Devonian Siliceous Mudstone – Upper Chert Formation</i> <i>Greyish black laminated chert and siliceous mudstone. Randomly-oriented to bedding-parallel bioturbation is common in the bottom of the unit. « lm chrt 75.00-95.00% », « btrb 0.10-2.00cm », Medium-light grey, sometimes darker. Siliceous and calcareous zones. Cherty bands from top to 26.8 m. Some 20-40 cm limestone clasts (not concretions). Classic calcite veining, very sparse. Largely barren other than that.</i> <i>« 26.80- 33.40 Turbidite. Sharp base at lower contact. Corase grained, slightly angular to slightly rounded fragments at the base; upward fining sequence. Therefore, uphole = younging direction. »</i> <i>« 53.50- 59.00 Fault FLT » « brco 10%»« flt bx 60%»« flt gg 15%»</i> <i>« 73.20- 73.30 Partial turbidite, with distorted contacts. No clear fininf direction. Only coarse grains present. »</i> <i>« 77.80- 78.00 Several cm-scale turbidites show uphole fining directions and sharp lower contacts. »</i> <i>« 81.30- 81.50 Partial turbidite. Slightly finer uphole, coarse at base. Sharp contacts sever rock features. »</i> <i>« 96.90- 107.90 Intensely broken fault zone. FLT »« brco 15%»« flt bx 20%»« flt gg 10%»</i> <i>« 118.90- 131.10 Fault zone; highly broken rock with completely crumbled sections. FLT»« brco 30%»« flt bx 30%»« flt gg 10%»</i>											

Selwyn Project Diamond Drill Log

Hole Number:
XYC-241

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		< @ 141.40 Bedding in faint pyrite lamination S0 TCA 75° > < @ 167.10 Bedding in faint pyrite lamination S0 TCA 65° > « 168.10- 170.60 Fault FLT »« brco 25%»« flt bx 25%»« flt ggq 15%» « 171.30- 172.00 Broken zone. Intensely fractured zone above fault. » « 172.00- 173.80 Fault FLT »« brco 60%»« flt bx 15%»« flt gg 15%» « 173.80- 191.60 Intensely fractured zone below fault » < @ 205.90 Bedding in faint calc-pyrite laminae S0 TCA 70° > < @ 219.40 Bedding in wispy pyrite laminae S0 TCA 75° > « 231.20- 264.30 Large fault zone. FLT »« brco 20%»« flt bx 30%»« flt gg 15%» « 277.80- 309.00 Large fault zone. FLT »« brco 5%»« flt bx 30%»« flt gg 15%»									
309.00	373.70	FLMD									
		FLMD – Flaggy Mudstone Formation Dark grey mudstone in the upper portions of the unit grading into light grey mudstone to siltstone. Contains abundant wispy bioturbation which ranges from randomly-oriented at the top of the unit to bedding-parallel throughout the majority of the unit. Darker upper section has a strong fetid odour along broken surfaces. « btrb 0.10-2.00cm », « cg xtl crns ca 1.00-5.00% 5.00-150.00cm », « crns py 1.00-5.00% 0.10-0.50mm », Non-typical intersection. Much of the unit is dark and uniform. It was mistaken as part of Backside at first, because it is not the continuous light grey									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-241

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		flaggy that is common. Sections that do contain good flaggy texture have been noted below. Upper Siliceous follows these sections immediately. It is possible that some or most of the unit could have been faulted away, as there are several faults in the unit large enough to do so, but this cannot be proven. « 309.00- 210.20 Core is medium-light grey, and has a slightly brecciated or flaggy appearance. It is not classic FLMD. Siliceous; no very little calcite. Qtz-calc v eining is noticeably more abundant than the fairly barren BSSM above. » « 314.10- 318.30 Pyrite blebs. Some are disseminated, some are concretions. All are 1-3 mm wide. Occasionally elongate. Contains lighter mudstone bands or concretions. » « 313.70- 314.20 Flaggy range. Slightly lighter grey. » « 321.00- 326.70 Flaggy range. » « 327.00- 336.20 Fault FLT »« brco 40%»« flt bx 30%»« flt gg 10%» « 336.20- 344.10 Broken zone » « 344.10- 362.50 Fault zone. FLT »« brco 10%»« flt bx 50%»« flt gg 15%» « 362.10- 373.70 Flaggy, lighter. Starts in fault. Lower contact transitional. »									
373.70	468.90	USMS	630701	467.00	468.00	1.00	0.01	0.09	1.00	5.00	0.11
		USMS – Upper Siliceous Mudstone	630702	468.00	468.90	0.90	0.01	0.21	1.00	5.00	0.05
		Consists of interlaminated dark grey to black mudstone and light to medium grey chert. Regionally, a 1m thick graptolite zone occurs 15m below the top of the upper unit, this is usable as a horizon. The USMS is divided into 3 units. The Lower Unit contains abundant limestone concretions and Galena and sphalerite micro-concretions occur locally near the base of this unit. « gra , lm chrt									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-241

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		-20.00% » , « cg xtl sph crns ca 5.00-20.00cm » , « bed chrt 10.00-15.00% » , Black (sometimes dark grey) mudstone with infrequent calcite stringers. Mostly siliceous. Disseminated pyrite throughout as well as in beds, stringers, and blebs. Not typical for this unit. Infrequent cherty banding. Fairly monotonous. Reminiscent of CCMS. Competent unit. No faulting. Disseminated pyrite beds contain disseminated calcite. There are disseminated calcite bands with the same wormy texture as the cherty bands. Becomes more "classic USMS" downhole. < @ 411.20 Bedding in disseminated pyrite-calcite beds S0 TCA 40° > « 427.70- 427.80 Fault FLT »« flt bx 70%»« flt gg 30%» < @ 431.80 Bedding in planar chert bands. S0 TCA 65° > < @ 441.20 Bedding in planar chert bands. S0 TCA 50° > < @ 447.30 Bedding in planar chert bands. 55° > « 457.00- 458.90 Fault. Core lost. About 55 cm of rubble recovered. FLT »« flt bx 50%»« flr gg 50%» « 458.90- 489.00 Broken zone »									
468.90	516.20	ACTM	630703	468.90	470.20	1.30	0.18	0.29	2.00	5.00	0.62
ACTM – Active Member			630704	470.20	471.00	0.80	0.04	0.02	1.00	5.00	2.00
			630705	471.00	473.70	2.70	0.01	0.14	1.00	5.00	0.07
			630706	473.70	473.80	0.10	0.01	0.01	1.00	5.00	2.00
			630707	473.80	474.10	0.30	0.01	0.04	1.00	5.00	0.25
			630708	474.10	474.40	0.30	0.04	0.01	1.00	5.00	8.00
			630709	474.40	477.00	2.60	0.01	0.24	1.00	5.00	0.04
			630710	477.00	479.30	2.30	0.11	1.80	1.00	70.00	0.06
			630711	477.00	479.30	2.30	0.13	1.64	1.00	60.00	0.08
=====			630712	479.30	479.70	0.40	1.45	5.80	4.00	180.00	0.25

Selwyn Project Diamond Drill Log

Hole Number:
XYC-241

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
The ACTM has 8 different facies: =====			630713	479.70	479.90	0.20	2.61	9.23	1.00	330.00	0.28
			630714	479.90	481.40	1.50	1.99	5.43	1.00	190.00	0.37
			630715	481.40	482.30	0.90	0.31	2.66	1.00	70.00	0.12
- GREY CHERT FACIES: Consists of laminated medium light grey to medium dark grey chert. Mineralization: 95-99% quartz and up to 5% secondary calcite.			630716	482.30	483.70	1.40	0.17	0.04	1.00	5.00	4.25
			630717	483.70	484.80	1.10	0.07	0.02	1.00	5.00	3.50
			630718	484.80	487.50	2.70	0.03	0.35	1.00	10.00	0.09
- WHITISH GREY ZN-PB MUDSTONE FACIES: Is a laminated cherty rock containing up to 70% sulphides. Mineralization: quartz, sphalerite and galena are the major minerals with only minor amounts of pyrite and locally calcite. Sedimentary diagenetic structures are common and well displayed in the facies, such as: lamination, pseudo-beds, calcite nodules & limestone nodules and abundant water escape structures. Most obvious structure in facies is cross-cutting veins containing massive sphalerite and galena with minor pyrite. They range in width from 0.5 to 10mm.			630719	487.50	488.20	0.70	2.06	13.84	1.00	390.00	0.15
			630720	488.20	488.20	0.00	0.01	0.01	1.00	5.00	1.00
			630721	488.20	489.00	0.80	0.57	2.11	1.00	60.00	0.27
			630722	489.00	490.00	1.00	0.01	0.05	1.00	5.00	0.20
			630723	490.00	491.00	1.00	0.04	0.18	1.00	5.00	0.22
			630724	491.00	492.40	1.40	0.64	2.33	1.00	80.00	0.27
			630725	492.40	493.50	1.10	1.09	1.37	1.00	40.00	0.80
			630726	493.50	494.80	1.30	1.44	3.37	1.00	110.00	0.43
			630727	494.80	496.30	1.50	1.12	3.98	1.00	110.00	0.28
- THIN BEDDED CHERTY MUDSTONE FACIES: Consists of rhythmic intercalated laminae of chert, carbonaceous mudstone and minor micrite. This facies contains significant amounts of Zn and Pb sulphides.			630728	496.30	497.80	1.50	1.07	3.26	1.00	100.00	0.33
			630729	497.80	498.80	1.00	0.97	4.11	1.00	130.00	0.24
			630730	498.80	498.80	0.00	6.01	6.59	71.00	180.00	0.91
			630731	498.80	499.80	1.00	1.19	6.54	1.00	200.00	0.18
- CHERTY MUDSTONE FACIES: Consists of a greyish black monotonous siliceous, carbonaceous mudstone. It is most typically found overlying the thin bedded calcareous mudstone facies.			630732	499.80	501.10	1.30	4.90	14.57	2.00	580.00	0.34
			630733	501.10	502.60	1.50	1.83	10.47	1.00	240.00	0.17
			630734	502.60	503.60	1.00	2.45	6.34	1.00	230.00	0.39
			630735	503.60	504.50	0.90	0.12	0.49	1.00	20.00	0.24
- THIN BEDDED CALCAREOUS MUDSTONE FACIES: Consists of laminated carbonaceous mudstone containing 20-40% calcite, 40-55% quartz and 10-20% muscovite. Sulphides occur in laminae. In the XY area it is usually the lowest facies in the section to contain laminated sulphides.			630736	504.50	506.40	1.90	0.66	1.07	1.00	50.00	0.62
			630737	506.40	507.20	0.80	0.14	0.01	1.00	20.00	28.00
			630738	507.20	507.60	0.40	0.02	0.06	1.00	5.00	0.33
			630739	507.60	509.00	1.40	0.47	2.91	1.00	90.00	0.16
			630740	509.00	510.10	1.10	0.53	1.40	1.00	40.00	0.38
- CALCAREOUS MUDSTONE FACIES: Consists of grey to greyish black monotonous, calcareous siliceous carbonaceous mudstone. There are no feathery calcite beds or pyrite-calcite blebs in the facies, making it easily distinguishable from the CCMS.			630741	509.00	510.10	1.10	0.92	2.32	1.00	60.00	0.40
			630742	510.10	511.60	1.50	0.30	0.26	1.00	5.00	1.15
			630743	511.60	513.00	1.40	0.75	0.65	1.00	20.00	1.15
			630744	513.00	513.30	0.30	5.66	6.53	12.00	220.00	0.87
			630745	513.30	513.80	0.50	0.50	3.18	1.00	130.00	0.16

Selwyn Project Diamond Drill Log

Hole Number:
XYC-241

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		- GRADED LIMESTONE FACIES: Is a laminated argillaceous limestone with intercalated carbonaceous limestone laminae. The main rock type in the facies is laminated limestone with laminae up to 0.1-7mm thick.	630746	513.80	514.10	0.30	0.01	0.01	1.00	30.00	2.00
			630747	514.10	514.50	0.40	0.03	0.07	1.00	20.00	0.43
			630748	514.50	516.20	1.70	0.01	0.12	1.00	30.00	0.08
		- LIGHT GREY BASAL LIMESTONE FACIES - LGLS: Consists of laminated argillaceous limestone. In the Anniv area it marks the end of the ACTM. It's not always present in the stratigraphy.									
		- BASAL FACIES: This is a highly contorted and locally foliated carbonaceous mudstone. Unlike the other facies it is not repeated higher in the member. It appears locally to contain the slip zone of a major slump. The facies has only been observed in the YX area. It is 0.1-2m thick. The facies consists of massive carbonaceous siliceous mudstone with lenses and laminae of contorted, slightly carbonaceous chert.									
		« 468.90- 470.20 Black siliceous mudstone. Trace mineralization. »									
		« 470.20- 471.00 Medium grey siliceous mudstone with faint lamination and calcite veins. No mineralization. »									
		« 471.00- 473.70 Black siliceous monotonous mudstone. Trace sphalerite. »									
		« 471.00- 473.00 Fault. Core lost and washed. FLT »« brco 60%»« flt bx 40%»									
		« 473.70- 473.80 Light grey, weakly bedded limestone. Barren. »									
		« 473.80- 474.10 Black siliceous mudstone. Barren. »									
		« 474.10- 474.40 Light and medium grey limestone with moderate bedding. Medium grained. Barren. »									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-241

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		« 474.40- 479.30 Black to dark grey siliceous carbonaceous mudstone. Trace sphalerite in weak laminae. »									
		« 474.40- 479.40 Fault FLT »« brco 35%»« flt bx 20%»« flt gg 5%»									
		« 479.30- 479.70 Black siliceous mudstone with mineralization in laminae. Niton: Pb 3.5%, Zn 2.8% »									
		« 479.70- 179.90 Medium-light grey siliceous mudstone without lamination. Massive. Niton: Pb 3.2%, Zn 6.5% »									
		« 479.90- 481.80 Black siliceous mudstone with frequent calcite veins and pyrite. Weak laminae contain mineralization. Niton: Pb 2.6%, Zn 2.1% »									
		« 479.90- 481.40 Broken zone »									
		« 481.40- 481.50 Light grey, medium grained limestone. Barren. »									
		« 481.50- 482.30 Dark grey, calcareous mudstone. Calcareous laminae with trace sphalerite. »									
		« 482.30- 483.70 Light grey, bedded, medium grained limestone. Barren. »									
		« 483.70- 484.80 Medium grey, highly calcareous mudstone. Weak lamination. Barren. »									
		« 484.80- 487.50 Dark grey to black, carbonaceous, calcareous mudstone. Trace sphalerite. »									
		« 485.20- 487.50 Fault. Core lost. FLT »« brco 20%»« flt bx 75%»« flt gg 5%»									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-241

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		« 487.50- 488.20 Dark grey, good grade. Mangled laminae. Looks better than it is. Niton: Pb 6.4%, Zn 2.3% »									
		« 488.20- 489.00 Light to medium grey limestone. Medium grained. Veined with calcite. Trace mineralization. »									
		« 489.00- 491.00 Very light grey, fine grained limestone. Trace mineralization. »									
		« 491.00- 492.40 Medium grey, calcareous mudstone. Weak lamination. Tiny calcite stringers. Niton: Pb 0%, Zn 0.8% »									
		« 492.40- 493.50 Medium grey, weakly laminated limestone with light grey, fine grained limestone clasts. Niton: Pb 0.5%, Zn 0.7% »									
		« 493.50- 494.80 Intercalated limestone and calcareous mudstone. Sphalerite in laminations, galena in stringers. Niton: Pb 1.9%, Zn 3.3% »									
		« 494.80- 499.80 Medium grey, fine grained limestone with medium-dark grey mudstone laminations. Sphalerite and galena disseminated and galena in fine stringers. Mudstone content increases downward. Niton: Pb 1.6%, Zn 3.4% »									
		« 499.80- 501.10 Light grey, medium grained dirty limestone intercalated with calcite veins and mudstone. High grade. Estimate 25% combined. »									
		« 501.10- 502.60 Medium dark grey calcareous mudstone with abundant sphalerite in laminae. Galena in small stringers with calcite. One small stringer also contains crystallized sphalerite. »									
		« 502.60- 503.60 Medium grey, dirty, fine grained limestone. Moderate laminations. Niton: Pb 1.3%, Zn 2.8% »									
		« 503.60- 504.50 Dark grey mudstone. Carbonaceous. No mineralization. »									

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		« 503.30- 511.20 Broken zone. »									
		« 504.50- 506.40 Dark grey, dirty limestone. Fine grained. Carbonaceous. Trace mineralization. »									
		« 506.40- 507.20 Light and medium grey, dirty limestone with some mudstone. Calcite beins. No mineralization. »									
		« 507.20- 507.60 Medium grey calcareous mudstone with weak laminations. No mineralization. »									
		« 507.60- 510.10 Dark grey-black silicious mudstone. Carbonaceous. Niton: Pb trace, Zn 1.7% »									
		« 509.00- 510.00 FLT »« Flt gg 5%»« Flt bx 15%»« Brco 80%»									
		« 510.10- 513.00 Light grey, weakly bedded, medium grained limestone. No mineralization. »									
		« 513.00- 513.30 Silicious medium grey mudstone. Trace mineralization. »									
		« 513.30- 513.80 Calcareous medium grey mudstone. Weak laminations. Niton: Pb 0.8%, Zn 3.2% »									
		« 513.80- 514.10 Light grey fine grained massive limestone. No mineralization. »									
		« 514.10- 514.50 Black calcareous carbonaceous mudstone. Very broken up. Some gouge present. No mineralization. »									
		« 514.50- 516.20 Medium grey limestone with trace mineralization. Quartz-calcite veins present. »									



Hole Number:
XYC-241

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

[illegible]

Diamond Drill Log

Comprehensive Report for Hole:

XYC-240

Hole No.: XYC-240	Depth: 194.00 m	Horizontal Length: 0.00 m	Project: 1710
Location Data:			
Property:	Selwyn Project	Claim Name:	X 14
Mining District:	Selwyn Basin	Grant Number:	Y 64539
Province/Territory:	Yukon		
UTM Co-Ordinates & Altitude of Drill Hole Collar:			
UTM Easting:	488887.79 m	True Azimuth:	224.0 °
UTM Northing:	6926191.83 m	Hole Angle:	-85.0 °
Elevation (m):	1594.13 m	NTS Name:	Placer Creek
		NTS Number:	105L06
Grid Co-Ordinates of Drill Hole Collar:			
Grid Easting (m):	0.00 m	Grid Name:	HP 06
Grid Northing (m):	0.00 m	Grid Type:	100m
Grid Azimuth:	284.0 °		
Dimond Drilling Contract:			
Drilled By:	CY-01	Date Drilling Start:	10/29/2010
		Date Finish:	11/02/2010
Diamond Drill Core:			
Logged By:	Graham Leroux / Helena	Date Logging Start:	11/07/2010
		Date Finish:	11/18/2010
Legend for Core Logging Codes: PAX			
Core Size:	NQ	Cemented:	Yes
Casing Depth:	6.90 m	Casing Pulled:	Yes
Water Depth:	0.00 m	Overburden Depth:	6.90 m
Level:		Section:	
		Drift:	

Selwyn Project

Diamond Drill Log

Survey Data for Hole

XYC-240

Hole Comments:

Sat, Oct 30 --- Total depth 23m in USMS. 6m of casing. They have a very bad leak in their exhaust manifold, no drilling last night, still on standby until repair parts coming .

=====

Sun, Oct 31 --- No drilling due to an exhaust leak. A repair kit came in yesterday afternoon, but it is supposed to set for 24 hours before being used.

=====

Mon, Nov 01 --- Total depth 68m in barren or low grade ATCM after a fault which goes from 55.5m-63m. Fault is 30% gouge, 40% broken core.

=====

Tue, Nov 02 --- "Shut down at 194m in CCMS. ACTM is from 68m to 149.5m There is a fault from 95-114m that is very broken and hard to identify, it appears to be CCMS, but should be included in the ACTM intersection for the time being. Will move to target #65 today."

<i>Depth</i>	<i>Dip</i>	<i>Azimuth</i>
0.00	-85.0	224.0
38.00	-85.1	224.7
128.00	-84.5	226.3
152.00	-84.1	223.6
194.00	-83.8	219.2

Selwyn Project Diamond Drill Log

Hole Number:
XYC-240

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
0.00	6.90	OVBR									
6.90	60.00	USMS	635151	15.10	15.60	0.50	0.04	0.04	1.00	20.00	1.00
<i>USMS – Upper Siliceous Mudstone</i> <i>Consists of interlaminated dark grey to black mudstone and light to medium grey chert. Regionally, a 1m thick graptolite zone occurs 15m below the top of the upper unit, this is usable as a horizon. The USMS is divided into 3 units. The Lower Unit contains abundant limestone concretions and Galena and sphalerite micro-concretions occur locally near the base of this unit. « gra , lm chrt -20.00% », « cg xtl sph crns ca 5.00-20.00cm », « bed chrt 10.00-15.00% »</i> <i>« 6.90- 60.00 Typical of unit. Variable amounts of chert, calcite, pyritic bands 2-7mm @5-10%. »</i> <i>« 12.00- 12.80 Well developed pseudotachylite, abundant fractures. Flt »« Flt gg 10%»« Flt bx 10%»« Brco 80%»</i> <i>« 12.80- 15.60 Dark grey-black cherty and pyritic mudstone. Typical of USMS. »</i> <i>« 15.60- 16.20 Laminated metalliferous mudstone. ~10% sphalerite, 7-10% galena. Light grey to brownish grey in colour. Laminated pyrite and calcite with sphalerite rich mud. Both sphalerite and galena are very fine grained. The interval of base metal mineralized mud occurs as a low angle stratigraphic contact. Rock is heavily fractured already, drilling often smashes it up-drillers are pushing too hard. Laminae are often contorted and faulted in block sections 2-4cm thick. Conformable limestone beds between 15-25cm typically are pervasive throughout the unit and comprise ~5-7% of rock interval. Much of this "USMS" unit is highly fractured and appears to crumble easily under removal from the core barrel tube. It is entirely possible the limestone layers actually represent large limestone fragments; however, many are conformable with the usms fabric.»</i> <i>« 16.20- 16.90 Typical USMS shoulder sample. »</i>			635152	15.60	16.20	0.60	1.00	7.94	8.00	250.00	0.13
			635153	16.20	16.90	0.70	0.04	0.13	1.00	20.00	0.31
			635154	58.00	59.00	1.00	0.03	0.16	1.00	20.00	0.19
			635155	59.00	60.00	1.00	0.01	0.05	1.00	20.00	0.20

Selwyn Project Diamond Drill Log

Hole Number:
XYC-240

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
< @ 16.40 S0 defined by depositional layers. S0 tca 55° > « 19.10- 19.90 Fine grained bluish-grey limestone. » « 19.90- 21.90 Blocky ground, highly fractured, calcareous mudstone. » < @ 21.90 S0 defined by laminae. S0 tca 60° > « 22.90- 23.20 Flt »« Flt gg 10%»« Flt bx 60%»« Brco 30%» « 23.90- 24.20 Flt »« Flt gg 15%»« Flt bx 60%»« Brco 25%» « 40.40- 55.60 Blocky ground, highly fractured. » « 55.60- 60.00 Flt »« Flt gg 25%»« Flt bx 50%»« Brco 25%»											
60.00	95.30	ACTM	635156	60.00	60.70	0.70	0.03	0.23	1.00	20.00	0.13
ACTM – Active Member			635157	60.70	62.40	1.70	0.29	0.44	2.00	30.00	0.66
			635158	62.40	63.00	0.60	4.90	6.63	3.00	240.00	0.74
The ACTM consists of a repetitive, possibly rhythmic, sequence of intercalated carbonaceous mudstone, cherty mudstone, chert and limestone and locally contains economically significant Zn and Pb sulphides (see bold marked facies), mainly in its sections with well developed lamination. Because of its heterogeneity, the member is distinctive and easily identified.			635159	63.00	63.70	0.70	0.43	14.12	1.00	550.00	0.03
			635160	63.70	64.70	1.00	0.08	0.29	1.00	10.00	0.28
			635161	63.70	64.70	1.00	0.08	0.85	1.00	30.00	0.09
			635162	64.70	65.90	1.20	0.01	0.01	1.00	5.00	1.00
			635163	65.90	66.30	0.40	0.31	0.54	2.00	20.00	0.57
			635164	66.30	67.60	1.30	0.01	0.01	1.00	5.00	1.00
=====			635165	67.60	68.50	0.90	0.03	0.23	1.00	10.00	0.13
The ACTM has 8 different facies:			635166	68.50	69.10	0.60	0.73	2.46	1.00	110.00	0.30
=====			635167	69.10	70.10	1.00	0.90	3.65	1.00	110.00	0.25
			635168	70.10	70.70	0.60	0.51	2.53	1.00	70.00	0.20
- GREY CHERT FACIES: Consists of laminated medium light grey to medium dark grey chert. Mineralization: 95-99% quartz and up to 5% secondary calcite.			635169	70.70	71.10	0.40	0.64	2.08	1.00	60.00	0.31
			635170	71.10	71.10	0.00	0.01	0.01	1.00	5.00	2.00
			635171	71.10	71.60	0.50	0.81	1.82	1.00	60.00	0.45
- WHITISH GREY ZN-PB MUDSTONE FACIES: Is a laminated cherty rock containing up			635172	71.60	72.10	0.50	0.70	3.08	1.00	120.00	0.23
to 70% sulphides. Mineralization: quartz, sphalerite and galena are the major											
			635173	72.10	72.90	0.80	8.39	21.59	6.00	920.00	0.39

Selwyn Project Diamond Drill Log

Hole Number:
XYC-240

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
minerals with only minor amounts of pyrite and locally calcite. Sedimentary diagenetic structures are common and well displayed in the facies, such as: lamination, pseudo-beds, calcite nodules & limestone nodules and abundant water escape structures. Most obvious structure in facies is cross-cutting veins containing massive sphalerite and galena with minor pyrite. They range in width from 0.5 to 10mm. - THIN BEDDED CHERTY MUDSTONE FACIES: Consists of rhythmic intercalated laminae of chert, carbonaceous mudstone and minor micrite. This facies contains significant amounts of Zn and Pb sulphides. - CHERTY MUDSTONE FACIES: Consists of a greyish black monotonous siliceous, carbonaceous mudstone. It is most typically found overlying the thin bedded calcareous mudstone facies. - THIN BEDDED CALCAREOUS MUDSTONE FACIES: Consists of laminated carbonaceous mudstone containing 20-40% calcite, 40-55% quartz and 10-20% muscovite. Sulphides occur in laminae. In the XY area it is usually the lowest facies in the section to contain laminated sulphides. - CALCAREOUS MUDSTONE FACIES: Consists of grey to greyish black monotonous, calcareous siliceous carbonaceous mudstone. There are no feathery calcite beds or pyrite-calcite blebs in the facies, making it easily distinguishable from the CCMS. - GRADED LIMESTONE FACIES: Is a laminated argillaceous limestone with intercalated carbonaceous limestone laminae. The main rock type in the facies is laminated limestone with laminae up to 0.1-7mm thick. - LIGHT GREY BASAL LIMESTONE FACIES - LGLS: Consists of laminated argillaceous limestone. In the Anniv area it marks the end of the ACTM. It's not always present in the stratigraphy.			635174	72.90	73.90	1.00	1.65	4.99	1.00	140.00	0.33
			635175	73.90	74.40	0.50	0.76	5.06	1.00	130.00	0.15
			635176	74.40	75.40	1.00	0.71	4.05	1.00	110.00	0.18
			635177	75.40	76.10	0.70	0.90	1.68	1.00	50.00	0.54
			635178	76.10	76.70	0.60	0.19	0.40	1.00	20.00	0.48
			635179	76.70	77.20	0.50	2.56	4.65	1.00	240.00	0.55
			635180	77.20	77.20	0.00	6.06	6.68	69.00	180.00	0.91
			635181	77.20	77.80	0.60	0.32	0.01	1.00	5.00	32.00
			635182	77.80	78.70	0.90	0.10	0.07	1.00	5.00	1.43
			635183	78.70	79.30	0.60	0.08	0.21	1.00	5.00	0.38
			635184	79.30	79.80	0.50	0.01	0.12	1.00	5.00	0.08
			635185	79.80	80.70	0.90	0.02	0.01	1.00	5.00	2.00
			635186	80.70	81.80	1.10	0.09	0.28	1.00	5.00	0.32
			635187	81.80	82.50	0.70	0.40	1.37	1.00	30.00	0.29
			635188	82.50	83.70	1.20	0.09	1.20	1.00	30.00	0.08
			635189	83.70	84.90	1.20	0.05	0.19	1.00	5.00	0.26
			635190	84.90	85.30	0.40	0.05	0.17	1.00	5.00	0.29
			635191	84.90	85.30	0.40	0.07	0.19	1.00	5.00	0.37
			635192	85.30	85.90	0.60	0.06	0.20	1.00	5.00	0.30
			635193	85.90	86.40	0.50	0.47	0.35	1.00	5.00	1.34
			635194	86.40	87.00	0.60	0.26	1.91	2.00	40.00	0.14
			635195	87.00	87.60	0.60	0.05	0.35	1.00	5.00	0.14
			635196	87.60	88.10	0.50	0.24	2.17	1.00	50.00	0.11
			635197	88.10	89.20	1.10	0.14	1.47	1.00	40.00	0.10
			635198	89.20	90.00	0.80	0.05	0.88	2.00	30.00	0.06
			635199	90.00	90.40	0.40	0.07	0.71	1.00	20.00	0.10
			635200	90.40	90.40	0.00	0.01	0.01	1.00	5.00	2.00
			635201	90.40	91.20	0.80	0.37	0.29	3.00	5.00	1.28
			635202	91.20	92.40	1.20	0.01	0.01	1.00	5.00	2.00
			635203	92.40	93.10	0.70	0.01	0.01	1.00	5.00	2.00
			635204	93.10	93.70	0.60	0.01	0.01	1.00	5.00	2.00
			635205	93.70	94.20	0.50	0.05	0.01	1.00	5.00	10.00
			635206	94.20	95.30	1.10	0.01	0.01	1.00	5.00	2.00

Selwyn Project Diamond Drill Log

Hole Number:
XYC-240

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		- BASAL FACIES: This is a highly contorted and locally foliated carbonaceous mudstone. Unlike the other facies it is not repeated higher in the member. It appears locally to contain the slip zone of a major slump. The facies has only been observed in the YX area. It is 0.1-2m thick. The facies consists of massive carbonaceous siliceous mudstone with lenses and laminae of contorted, slightly carbonaceous chert. « 60.00- 60.70 Muddy limestone, graded beds, blocky ground. » « 60.70- 63.00 Blocky ground. Laminated pyritic weakly mineralized mudstone. Some sections of massive pyrite 3-15cm thick. Stringer and blebby galena cores some qt-cal veins, with an outer vein of coarse sphalerite (<1%). » « 63.00- 63.70 Light grey laminated brown, sphalerite rich laminae, with trace stringer and blebby galena. Discordant dissolution seams are composed of sphalerite enriched mud. Pb ~ 0.34%, Zn ~ 10.3% » « 63.70- 65.40 Intercalated mud-rich laminated limestone, metalliferous mudstone and calcareous mudstone. Pyrite is most common sulphide, occurs as stringers and disseminations. Calcite-qt veins often brecciate and incorporate angular fragments of host rock. Limestone concretions and framboidal pyrite are also common. » « 65.90- 66.30 Laminated calcareous mudstone, limestone, and metalliferous mudstone. Concentrations of pyrite can be 30-6% through laminated sections 2-7cm thick. » « 66.30- 69.10 Poorly laminated, medium to fine grained graded limestone with pervasive cal-qt veins, often which are associated with pyrite. Trace amounts of distorted metalliferous mudstone mixed interstitially to large limestone blocks 30cm-100cm in diameter. » « 69.10- 70.10 Well laminated and block fractured very silicious, cherty metalliferous mudstone. Medium grey to black laminae 1-3mm thick									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-240

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		typically. » « 70.10- 72.10 Cross-bedded and contorted graded limestone laminae. Calcite and minor quartz often marks the contact between limestone blocks 20cm-1m that have been moved around a bit. Mineralization is mostly of sphalerite enriched laminae with trace specular galena. » « 72.10- 72.90 Laminated very-calcareous mudstone to limestone, light bluish-grey in colour, abundant calcite rich laminae. Stringer galena with trace amounts of coarse secondary sphalerite. Pyrite content increased down interval. » « 72.90- 75.40 Highly contorted metalliferous silicious mudstone with irregular-shaped laminated limestone clasts. The contortions of folded laminae are fractured by a systematic cleavage which tends to cause and offset blocky appearance. » « 75.40- 80.70 Laminated to massive silicious dark-grey pyritic mudstone. Blebs of py, galena, cal, qt (2-10mm diameter) are pervasive throughout in trace amounts. Massive micro-crystalline pyrite sections are up to 10cm thick and deformed into irregular fold patterns. Scattered limestone clasts throughout, also cal-qt veins throughout. Only minor sections with any base metal mineralization, even those are not particularly high-grade. » « 80.70- 82.50 Interval of carbonaceous and slightly silicious mudstone with calcic and cherty wormy bands 3-6mm thick, very similar in style to USMS. Calcite brecciated pyrite beds can be seen in the lower part of the interval. Calcite+ qt veining is increased through the range, (up to 5-10% in some places). Laminated limestone clasts are often rimmed with a milky white calcite. » « 82.50- 86.40 Thickly laminated to thinly bedded, graded limestone with minor mud-rich sections. Framboidal pyrite occurs in discontinuously pyritic zones. Calcite veining is relatively minor throughout. »									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-240

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
« 84.90- 85.30 Deformed along S0, this limestone has been weakly brecciated along S0 during deformation. » « 86.40- 90.40 Dark-grey laminated calcareous mudstone resembling appearance of CCMS. Pyritic pseudobeds caused from disseminated pyrite is common. Wispy conformable calcite, also calcite remineralized stylolites. Trace disseminated-blebby galena occurs in specs rimmed with calcite <3-4mm diameter» « 90.40- 91.20 Contorted chert, calcic and muddy bands 3-6mm thick, quite pyritic (2-7%). This interval resembles very closely to typical USMS. » « 91.20- 93.10 Strongly foliated, laminated limestone clastic interbedded limestone between light and medium grey in colour. » « 93.10- 95.30 Calcite and qt laminae breccia rock. ~50% calcite and qt and ~50% laminated limestone. Discontinuous patchy zones of strongly disseminated pyrite. Minor patchy mudstone sections often see increases in pyrite content. »											
95.30	116.00	FLT	635207	95.30	96.90	1.60	0.01	0.23	1.00	5.00	0.04
« 95.30- 115.00 Through this fault zone the rock type consists of silicious and cherty variably calcareous mudstone with limestone concretions, typical of the USMS unit. The interval is highly fractured and has rare pseudo-beds of pyrite. No visible base metal mineralization, or any significant results with the NITON XRF machine. Bottom contact with "ACTM" is marked by a low angle change in S0 and a calcite-qt vein ~1cm thick. FLT»« Flt gg 15%»« Flt bx 20%»« Brco 65%»			635208	96.90	97.60	0.70	0.01	0.19	1.00	5.00	0.05
			635209	113.80	115.10	1.30	0.08	0.71	1.00	30.00	0.11
			635210	115.10	115.10	0.00	1.49	4.35	26.00	280.00	0.34
			635211	115.10	116.00	0.90	0.12	0.75	1.00	40.00	0.16
116.00	151.20	ACTM	635212	116.00	116.40	0.40	2.91	6.65	1.00	440.00	0.44
ACTM – Active Member The ACTM consists of a repetitive, possibly rhythmic, sequence of intercalated carbonaceous mudstone, cherty mudstone, chert and limestone and locally			635213	116.40	116.90	0.50	2.16	9.62	3.00	390.00	0.22
			635214	116.90	117.40	0.50	2.08	20.15	1.00	920.00	0.10
			635215	117.40	118.40	1.00	3.55	25.16	1.00	1180.00	0.14
			635216	118.40	119.10	0.70	3.08	4.83	1.00	190.00	0.64

Selwyn Project Diamond Drill Log

Hole Number:
XYC-240

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
contains economically significant Zn and Pb sulphides (see bold marked facies), mainly in its sections with well developed lamination. Because of its heterogeneity, the member is distinctive and easily identified.			635217	119.10	119.80	0.70	0.29	2.39	1.00	70.00	0.12
			635218	119.80	120.90	1.10	1.13	5.50	1.00	150.00	0.21
			635219	120.90	121.40	0.50	1.20	2.71	2.00	70.00	0.44
			635220	121.40	122.20	0.80	0.57	0.85	1.00	20.00	0.67
=====			635221	121.40	122.20	0.80	0.26	0.81	1.00	20.00	0.32
The ACTM has 8 different facies:			635222	122.20	123.10	0.90	0.08	0.77	1.00	20.00	0.10
=====			635223	123.10	123.70	0.60	0.18	0.97	2.00	30.00	0.19
- GREY CHERT FACIES: Consists of laminated medium light grey to medium dark grey chert. Mineralization: 95-99% quartz and up to 5% secondary calcite.			635224	123.70	124.20	0.50	0.85	5.35	1.00	160.00	0.16
			635225	124.20	124.70	0.50	0.06	0.03	1.00	5.00	2.00
			635226	124.70	125.40	0.70	0.09	0.13	1.00	5.00	0.69
			635227	125.40	126.10	0.70	0.31	0.55	1.00	10.00	0.56
- WHITISH GREY ZN-PB MUDSTONE FACIES: Is a laminated cherty rock containing up to 70% sulphides. Mineralization: quartz, sphalerite and galena are the major minerals with only minor amounts of pyrite and locally calcite. Sedimentary diagenetic structures are common and well displayed in the facies, such as: lamination, pseudo-beds, calcite nodules & limestone nodules and abundant water escape structures. Most obvious structure in facies is cross-cutting veins containing massive sphalerite and galena with minor pyrite. They range in width from 0.5 to 10mm.			635228	126.10	126.80	0.70	1.02	2.20	1.00	60.00	0.46
			635229	126.80	127.60	0.80	0.80	2.76	1.00	70.00	0.29
			635230	127.60	127.60	0.00	0.01	0.01	1.00	5.00	2.00
- THIN BEDDED CHERTY MUDSTONE FACIES: Consists of rhythmic intercalated laminae of chert, carbonaceous mudstone and minor micrite. This facies contains significant amounts of Zn and Pb sulphides.			635231	127.60	128.60	1.00	1.45	4.51	1.00	120.00	0.32
			635232	128.60	129.00	0.40	1.88	8.82	1.00	240.00	0.21
			635233	129.00	129.50	0.50	2.49	7.29	1.00	190.00	0.34
			635234	129.50	130.30	0.80	0.92	2.03	1.00	50.00	0.45
- CHERTY MUDSTONE FACIES: Consists of a greyish black monotonous siliceous, carbonaceous mudstone. It is most typically found overlying the thin bedded calcareous mudstone facies.			635235	130.30	130.70	0.40	0.98	6.77	3.00	160.00	0.14
			635236	130.70	131.30	0.60	0.34	0.38	1.00	5.00	0.89
			635237	131.30	131.80	0.50	1.98	8.01	1.00	180.00	0.25
			635238	131.80	132.40	0.60	0.74	8.66	1.00	210.00	0.09
- THIN BEDDED CALCAREOUS MUDSTONE FACIES: Consists of laminated carbonaceous mudstone containing 20-40% calcite, 40-55% quartz and 10-20% muscovite. Sulphides occur in laminae. In the XY area it is usually the lowest facies in the section to contain laminated sulphides.			635239	132.40	132.90	0.50	1.10	11.19	1.00	260.00	0.10
			635240	132.90	132.90	0.00	6.14	6.68	70.00	190.00	0.92
			635241	132.90	133.40	0.50	0.24	1.39	1.00	40.00	0.17
			635242	133.40	134.00	0.60	1.45	6.98	1.00	190.00	0.21
			635243	134.00	134.70	0.70	0.32	2.08	1.00	40.00	0.15
			635244	134.70	135.70	1.00	0.04	0.02	1.00	5.00	2.00
			635245	135.70	136.80	1.10	0.01	0.04	1.00	5.00	0.25
			635246	136.80	137.30	0.50	0.03	0.31	1.00	5.00	0.10
			635247	137.30	138.50	1.20	0.08	0.15	1.00	5.00	0.53
			635248	138.50	139.00	0.50	1.97	0.26	4.00	5.00	7.58
			635249	139.00	139.50	0.50	0.30	1.63	2.00	30.00	0.18

Selwyn Project Diamond Drill Log

Hole Number:
XYC-240

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
- CALCAREOUS MUDSTONE FACIES: Consists of grey to greyish black monotonous, calcareous siliceous carbonaceous mudstone. There are no feathery calcite beds or pyrite-calcite blebs in the facies, making it easily distinguishable from the CCMS.			635250	139.50	140.20	0.70	0.21	0.17	1.00	5.00	1.24
			634251	139.50	140.20	0.70	0.16	0.15	1.00	5.00	1.07
			634252	140.20	141.20	1.00	0.19	0.86	1.00	20.00	0.22
			634253	141.20	141.60	0.40	0.22	0.31	1.00	5.00	0.71
- GRADED LIMESTONE FACIES: Is a laminated argillaceous limestone with intercalated carbonaceous limestone laminae. The main rock type in the facies is laminated limestone with laminae up to 0.1-7mm thick.			634254	141.60	142.20	0.60	0.59	3.68	2.00	80.00	0.16
			634255	142.20	143.00	0.80	0.08	0.32	1.00	5.00	0.25
			634256	143.00	143.50	0.50	0.02	0.07	1.00	5.00	0.29
			634257	143.50	144.20	0.70	0.10	0.33	1.00	5.00	0.30
- LIGHT GREY BASAL LIMESTONE FACIES - LGLS: Consists of laminated argillaceous limestone. In the Anniv area it marks the end of the ACTM. It's not always present in the stratigraphy.			634258	144.20	144.80	0.60	1.37	1.49	5.00	40.00	0.92
			634259	144.80	145.50	0.70	0.18	0.84	1.00	20.00	0.21
			634260	145.50	145.50	0.00	0.01	0.01	1.00	5.00	2.00
- BASAL FACIES: This is a highly contorted and locally foliated carbonaceous mudstone. Unlike the other facies it is not repeated higher in the member. It appears locally to contain the slip zone of a major slump. The facies has only been observed in the YX area. It is 0.1-2m thick. The facies consists of massive carbonaceous siliceous mudstone with lenses and laminae of contorted, slightly carbonaceous chert.			634261	145.50	146.30	0.80	0.40	1.30	2.00	10.00	0.31
			634262	146.30	147.20	0.90	0.39	1.91	4.00	40.00	0.20
			634263	147.20	147.90	0.70	0.06	0.92	1.00	10.00	0.07
			634264	147.90	149.30	1.40	1.31	0.56	6.00	5.00	2.34
			634265	149.30	149.70	0.40	0.27	0.03	1.00	5.00	9.00
			634266	149.70	150.60	0.90	0.01	0.01	1.00	5.00	2.00
			634267	150.60	151.20	0.60	0.01	0.01	1.00	5.00	2.00
« 116.00- 119.10 Interlaminated light grey chert with sphalerite laminae and interstitial galena. Discordant dissolution seams are orthogonal to S0 and abundant. Pyritic and mud laminae are subordinate in volume to chert. Pyrite has a tendency to blow out in irregular splotches up to 5cm wide- they are commonly associated with recrystallized qt-cal. Zones with increased calcite veining, includeing veinlet swarms have a tendency to crumble under the drill pressure. Relatively high base metal grades. »											
« 118.40- 120.90 Flt »« Flt gg 25%»« Flt bx 15%»« Brco 60%»											
« 119.10- 120.90 Mud-rich, medium grained limestone. Interval is in a fractured zone. Laminated limestone clasts with irregular boundaries (2-7cm). Fairly low grade base metals to barren. »											

Selwyn Project Diamond Drill Log

Hole Number:
XYC-240

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		« 120.90- 124.20 Sequence from top to bottom: Laminated limestone, with irregular cal-qt veins. Calcareous and silicious concretionary mudstone weakly calcareous silicious mudstone. Silicious dark grey laminated mudstone with increaseing pyrite content downhole. Brecciated ground. Laminated base metalliferous mudstone with abundant pyrite laminae. » « 124.20- 128.60 Well laminated silicious and pyritic mudstone with ~50% by volume laminated limestone concretions. Through this limestone clastic interval there are two sequences of increasing base metal and sulphide laminae downhole. At the base of each sequence base metals are at a maximum and galena may concentrate enough to form stringers. At the top of each depositional sequence there is an increase in calcite and quartz veining, also calcareous mudstone and limestone is more abundant in the upper part of the sequence. Characteristic features of this unit are abundant rounded limestone clasts and planar laminated mudstone. » « 128.60- 134.00 This interval is also characterized by two depositional packages, showing a similar distribution of minerology in each case. The upper part of the sequence has laminated limestone and occasionally sphalerite enriched laminae and galena in cal-qt stringers. Further down, laminated chert and metal sulphides are contorted and comingled with calcareous laminae. Metal sulphide laminae in general increase down-section until eventually concentrating into a metalliferous mudstone. In the lower parts of each sequence, limestone clasts and pyritic conretions become more prominent. » « 134.00- 136.80 Light-grey planar laminated limestone with some interbedded mudstone. Limestone clasts up to ~6cm within mudstone. Limestone is barren (according to Niton), with very little Zn mineralization in mudstone. Pyrite blebs and open fracture fill with calcite. » « 136.80- 142.20 Predominantly dark-grey silicious mudstone with layers of conformable limestone ~5-20cm thick. Laminations are deformed with the base of this interval (at limestone) becoming more planar. Some pyritic laminae and blebs, as well as contorted or 'wormy' calcite veins that are mostly									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-240

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
conformable to bedding. Generally very low amounts of Zn + Pb mineralization (up to 0.86% Zn, 0.6% Pb). Galena vein ~4mm thick at bedding contact between limestone and mudstone. »											
« 142.20- 144.80 Medium to light grey limestone and muddy limestone. Calcite concretions at 143.5m. Laminations are planar with a secondary foliation on top. Upper and lower contacts are marked by calcite + pyrite veining. Euhedral pyrite also found, in larger amounts towards the base of the unit. Lighter limestone areas are barren. Muddier, darker areas have weak mineralization. »											
« 144.80- 149.30 Medium-to-dark grey mudstone. Near the top of section, it is calcareous, becoming weakly calcareous, and then silicious down section. Some interbedded limestone ~15cm thick, slowly grading into mudstone. Laminations are generally planar, and calcite veins conformable. Pyritic laminae present. Near bottom of the interval, calcic fragments parallel to bedding appear. Pyrite and calcite blebs are also present, and deform calcite veining around them. Disseminated pyrite up to 2%, with rock becoming more sulphidic down section. »											
« 149.30- 151.20 Basal limestone unit. Light-to-medium grey, planar, finely laminated limestone. Close to upper and lower contacts the mud component increases. Upper and lower contacts are marked by ~15-20cm of calcite breccia. Fragments in breccia are black, angular, soft, have a metallic-to-vitreous lustre, and do not react to HCl(mudstone with lots of graphite?). Niton shows they are high in Ni and V. Also at the bottom contact is a pyrite bleb. Entire section is barren. »											
151.20	194.00	CCMS	634268	151.20	152.00	0.80	0.03	0.08	3.00	5.00	0.38
CCMS – Calcareous Mudstone			634269	152.00	152.60	0.60	0.10	1.12	2.00	60.00	0.09
			634270	152.60	152.60	0.00	1.49	4.40	28.00	280.00	0.34
Massive, calcareous, carbonaceous, dark grey mudstone. Most of the member is massive, but rare poorly defined bedding and pyrite-calcite micro-concretions are present. Most diagnostic structures are feathery calcite beds (=thin calcite-cemented concretions, many of them contain pyrite cores) and calcite pseudo-beds (= fibrous calcite vein parallel to bedding).			634271	152.60	153.70	1.10	0.14	0.34	1.00	20.00	0.41

Selwyn Project Diamond Drill Log

Hole Number:
XYC-240

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		« lm ca 5.00-10.00mm », « nodules py -3.00% 2.00-20.00mm » « 151.20- 187.00 Dark-grey to black planar laminated mudstone. Predominantly silicious to weakly calcareous. There are layers and sections of more calcareous mudstone. Upper contact has ~30cm section of a high concentration of pyrite blebs ~5-7mm diameter, in association with contorted calcite veins. Very low grade mineralization (Pb+Zn <1%) near upper contact. Where visible, sequences appear normally graded. Throughout section are numerous thin to ~1.5cm thick pyritic laminae, as well as pyrite blebs and disseminated pyrite up to 2%. Periodic, consistent, planar, qt-cal veins ~2-5mm thick- almost orthogonal to bedding. Also present are calcic fragments aligned along S0. Depositional contacts are marked by deformed carbonate layers. Also seen are some remineralized cal-py stylolites. » < @ 161.80 S0 defined by laminae. S0 tca 74° > < @ 173.80 S0 defined by laminae. S0 tca 65° > < @ 175.30 S0 defined by calcic pyritic laminae S0 tca 23° > < @ 179.70 Qtz-cal vein set tca 36° > « 180.80- 187.00 Multiple faults in CCMS. Rock is heavily fractured, calcareous to weakly calcareous mudstone. Flt»« Flt gg 10%» « Flt bx 30%»« Brco 50%» « 187.00- 194.00 Dark-grey to black CCMS, silicious with some weakly calcareous. Heavily veined by calcite and some qtz. Veins are contorted, interconnected, and vary from <1mm to 5cm, brecciating the mudstone in places. »									
194.00	194.00	EOH									

Selwyn Project

Diamond Drill Log

Comprehensive Report for Hole:

XYC-239

Hole No.: XYC-239	Depth: 221.00 m	Horizontal Length: 0.00 m	Project: 1710
Location Data:			
Property:	Selwyn Project	Claim Name:	X 14
Mining District:	Selwyn Basin	Grant Number:	Y 64539
Province/Territory:	Yukon		
UTM Co-Ordinates & Altitude of Drill Hole Collar:			
UTM Easting:	488887.45 m	True Azimuth:	210.0 °
UTM Northing:	6926191.47 m	Hole Angle:	-70.5 °
Elevation (m):	1594.17 m	NTS Name:	Placer Creek
		UTM Datum:	NAD 83
		UTM Grid Zone:	9
		NTS Number:	105L06
Grid Co-Ordinates of Drill Hole Collar:			
Grid Easting (m):	0.00 m	Grid Name:	HP 06
Grid Northing (m):	0.00 m	Grid Type:	100m
Grid Azimuth:	270.0 °		
Dimond Drilling Contract:			
Drilled By:	CY-01	Date Drilling Start:	10/25/2010
		Date Finish:	10/29/2010
Diamond Drill Core:			
Logged By:	Kate Cameron / Graham	Date Logging Start:	11/04/2010
		Date Finish:	
Legend for Core Logging Codes: PAX			
Core Size:	NQ	Cemented:	Yes
Casing Depth:	6.00 m	Casing Pulled:	Yes
Water Depth:	0.00 m	Overburden Depth:	6.00 m
Level:	Section:	Drift:	

Selwyn Project

Diamond Drill Log

Survey Data for Hole

XYC-239

Hole Comments:

Tue, Oct 26 --- Yesterday moved to target #57 for XYC-239. Currently at 11m in USMS. 6m of casing. Drill settled last night and had to be lifted up, it is stable now with runoff directed away from the skids.

=====

Wed, Oct 27 ---At 53m in USMS. Lost return at the end of dayshift yesterday at 50m. Night shift pumped G-stop and still no return. They put 15 bags of cement down to try and seal the hole, they are waiting for that to set and will drill again this afternoon

=====

Thu, Oct 28 --- Total depth 101m in USMS. The cementing worked and they once again have return, the 15 bags had filled right to the top of the hole

=====

Fri, Oct 29 --- Shut down this morning at 221m in CCMS. The intersected active member from 125m-146m. They are going to test, cement and change dip to -85 degrees, target #58

<i>Depth</i>	<i>Dip</i>	<i>Azimuth</i>
0.00	-70.5	210.0
110.00	-69.6	213.2
152.00	-69.1	210.9
200.00	-68.8	211.3
221.00	-68.7	211.8

Selwyn Project Diamond Drill Log

Hole Number:
XYC-239

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
0.00	6.00	OVBR									
6.00	125.30	USMS	635101	123.20	124.00	0.80	0.32	0.16	2.00	5.00	2.00
USMS – Upper Siliceous Mudstone Consists of interlaminated dark grey to black mudstone and light to medium grey chert. Regionally, a 1m thick graptolite zone occurs 15m below the top of the upper unit, this is usable as a horizon. The USMS is divided into 3 units. The Lower Unit contains abundant limestone concretions and Galena and sphalerite micro-concretions occur locally near the base of this unit. « gra , lm chrt -20.00% », « cg xtl sph crns ca 5.00-20.00cm », « bed chrt 10.00-15.00% » « 6.00- 125.30 Typical. Silicious, some calcareous sections. Cherty banding shows "wormy" form. Broken up/fissile unit. In general: Spotted, conformable framboidal pyrite (0.1-2%). Intercalated, mud-brecciated medium grain limestone, scouring basae. Soft sediment deformation is common. Limestone layers resist interval (plane-parallel) failure. Stylolites are commonly remineralized with cal-qt. +/- pyrite. Many limestone layers are graded normally. Slick-n-lines develop on many S0 planes in carbonaceous sections. Calcite concentrations occur at base of limestone layers. In areas where bulk iron content is high, the qt tends to dominate as fluid, with minor calcite. Laminated in highly variable fashion ~107.5m. Heavily contorted calcite and qt, deformed rounded limestone clasts. » « 16.60- 17.00 Pure calcite vein. Sharp contacts. » « 30.30- 30.80 Medium grained, internally laminated limestone. Light grey. » « 33.90- 34.60 Coarse massive med grey limestone. » « 43.10- 56.50 Broken up fault zone. Flt »« Flt gg 15%»« Flt bx 25%»«			635102	124.00	124.50	0.50	0.01	0.01	1.00	5.00	2.00
			635103	124.50	125.30	0.80	0.20	0.61	2.00	20.00	0.33

Selwyn Project Diamond Drill Log

Hole Number:
XYC-239

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
Brco 20%» « 50.60- 56.00 Calcite veins dominate. One section of qtz vein ~30cm wide. » « 81.70- 82.10 Flt »« Flt gg 10%»« Flt bx 80%»« Brco 10%» « 84.10- 84.60 Flt »« Flt gg 60%»« Flt bx 10%»« Brco 30%» « 97.70- 98.00 Flt »« Flt bx 100%» « 98.00- 98.50 Recrystallized limestone. » « 98.60- 101.10 Flt »« Flt gg 10%»« Flt bx 30%»« Brco 60%» « 101.10- 125.30 Typical USMS as described, no major faulting. Minor laminated zones have increases in pyrite. »											
125.30	144.20	ACTM	635104	125.30	125.60	0.30	1.88	7.58	3.00	330.00	0.25
ACTM – Active Member			635105	125.60	126.00	0.40	1.56	5.94	3.00	200.00	0.26
The ACTM consists of a repetitive, possibly rhythmic, sequence of intercalated carbonaceous mudstone, cherty mudstone, chert and limestone and locally contains economically significant Zn and Pb sulphides (see bold marked facies), mainly in its sections with well developed lamination. Because of its heterogeneity, the member is distinctive and easily identified. ===== The ACTM has 8 different facies: ===== - GREY CHERT FACIES: Consists of laminated medium light grey to medium dark grey chert. Mineralization: 95-99% quartz and up to 5% secondary calcite. - WHITISH GREY ZN-PB MUDSTONE FACIES: Is a laminated cherty rock containing			635106	126.00	126.40	0.40	3.13	12.40	5.00	440.00	0.25
			635107	126.40	127.00	0.60	5.96	15.77	4.00	540.00	0.38
			635108	127.00	127.50	0.50	1.57	7.50	3.00	200.00	0.21
			635109	127.50	128.10	0.60	0.55	4.50	1.00	100.00	0.12
			635110	128.10	128.70	0.60	0.11	0.86	1.00	20.00	0.13
			635111	128.10	128.70	0.60	0.21	0.73	1.00	20.00	0.29
			635112	128.70	129.80	1.10	0.10	0.82	1.00	20.00	0.12
			635113	129.80	130.70	0.90	2.96	3.02	3.00	80.00	0.98
			635114	130.70	131.30	0.60	0.60	2.55	2.00	80.00	0.24
			635115	131.30	132.10	0.80	1.11	4.67	3.00	140.00	0.24
			635116	132.10	132.80	0.70	0.46	2.09	1.00	60.00	0.22
			635117	132.80	133.40	0.60	0.90	3.26	1.00	90.00	0.28
			635118	133.40	133.90	0.50	2.01	7.05	3.00	220.00	0.29
			635119	133.90	134.50	0.60	1.79	12.75	4.00	310.00	0.14
			635120	134.50	134.50	0.00	0.01	0.07	1.00	5.00	0.14

Selwyn Project Diamond Drill Log

Hole Number:
XYC-239

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
up to 70% sulphides. Mineralization: quartz, sphalerite and galena are the major minerals with only minor amounts of pyrite and locally calcite. Sedimentary diagenetic structures are common and well displayed in the facies, such as: lamination, pseudo-beds, calcite nodules & limestone nodules and abundant water escape structures. Most obvious structure in facies is cross-cutting veins containing massive sphalerite and galena with minor pyrite. They range in width from 0.5 to 10mm. - THIN BEDDED CHERTY MUDSTONE FACIES: Consists of rhythmic intercalated laminae of chert, carbonaceous mudstone and minor micrite. This facies contains significant amounts of Zn and Pb sulphides. - CHERTY MUDSTONE FACIES: Consists of a greyish black monotonous siliceous, carbonaceous mudstone. It is most typically found overlying the thin bedded calcareous mudstone facies. - THIN BEDDED CALCAREOUS MUDSTONE FACIES: Consists of laminated carbonaceous mudstone containing 20-40% calcite, 40-55% quartz and 10-20% muscovite. Sulphides occur in laminae. In the XY area it is usually the lowest facies in the section to contain laminated sulphides. - CALCAREOUS MUDSTONE FACIES: Consists of grey to greyish black monotonous, calcareous siliceous carbonaceous mudstone. There are no feathery calcite beds or pyrite-calcite blebs in the facies, making it easily distinguishable from the CCMS. - GRADED LIMESTONE FACIES: Is a laminated argillaceous limestone with intercalated carbonaceous limestone laminae. The main rock type in the facies is laminated limestone with laminae up to 0.1-7mm thick. - LIGHT GREY BASAL LIMESTONE FACIES - LGLS: Consists of laminated argillaceous limestone. In the Anniv area it marks the end of the ACTM. It's not always											
			635121	134.50	135.40	0.90	2.47	4.87	2.00	140.00	0.51
			635122	135.40	136.10	0.70	0.77	3.30	1.00	100.00	0.23
			635123	136.10	136.40	0.30	11.32	21.16	14.00	640.00	0.53
			635124	136.40	136.90	0.50	13.73	34.31	11.00	1130.00	0.40
			635125	136.90	137.20	0.30	8.40	26.75	6.00	770.00	0.31
			635126	137.20	137.90	0.70	2.47	7.69	4.00	250.00	0.32
			635127	137.90	138.40	0.50	7.83	25.08	4.00	900.00	0.31
			635128	138.40	138.70	0.30	8.23	29.72	6.00	1040.00	0.28
			635129	138.70	139.00	0.30	1.04	4.51	1.00	140.00	0.23
			635130	139.00	139.00	0.00	1.48	2.96	18.00	180.00	0.50
			635131	139.00	139.50	0.50	8.15	32.70	4.00	1150.00	0.25
			635132	139.50	140.10	0.60	6.64	24.18	3.00	890.00	0.27
			635133	140.10	141.10	1.00	6.67	23.74	1.00	900.00	0.28
			635134	141.10	141.90	0.80	0.10	0.17	1.00	5.00	0.59
			635135	141.90	142.90	1.00	0.68	0.40	1.00	10.00	1.70
			635136	142.90	143.80	0.90	0.09	0.56	1.00	20.00	0.16
			635137	143.80	144.20	0.40	0.12	0.27	1.00	5.00	0.44

Selwyn Project Diamond Drill Log

Hole Number:
XYC-239

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		present in the stratigraphy. - BASAL FACIES: This is a highly contorted and locally foliated carbonaceous mudstone. Unlike the other facies it is not repeated higher in the member. It appears locally to contain the slip zone of a major slump. The facies has only been observed in the YX area. It is 0.1-2m thick. The facies consists of massive carbonaceous siliceous mudstone with lenses and laminae of contorted, slightly carbonaceous chert. « 125.30- 126.40 Finely laminated metalliferous mudstone. Laminae are 1-4mm thick, with variable amounts of brownish sphalerite and fine-grained pyrite, very fine grained pyrite, very fine grained interstitial 3-8mm thick are often associated with calcite and quartz. Highly metalliferous depositional layers ~30cm thick have been broken out for sampling against calcareous laminated mudstone. » « 126.40- 128.10 Intercalated, high-grade, brownish contorted metalliferous mudstone with lower grade laminated calcareous mudstone. Galena is often occurring in a discordant fashion. Blocky interval, difficult to locate mineralization domains precisely. Abundant disseminated pyrite through galena rich intervals. Minor fault breccia throughout (<15cm thick). » « 128.10- 136.10 Intercalated dark-grey calcareous mudstone with mud-rich laminated limestone. Increases of calcite tends to occur at boundaries between limestone and mudstone. Abundant rounded limestone inclusions, may or may not be laminated, they commonly distort the already contorted laminae. Patchy occurrences of laminated base metal-rich mudstone 2-7cm thick. Much of the mudstone has undergone normal-sense block faulting, fractures of which are avenues for sulphide minerals. Blebs of coarse galena distort sphalerite and pyrite-rich laminae and occur as discordant splotches in metalliferous zones only. » « 136.10- 136.40 Wavy fine metalliferous mudstone, sphalerite and pyrite enriched laminae with coarser grained galena occurring as stringers in the axial plane of folded mudstone. Galena appears to be the cause of much of the laminae									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-239

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
deformation. »											
« 136.40- 137.20 High grade, light grey laminated galena, brown mud, grey and dark grey mud, sphalerite is yellowish and has later stage grain size increases (~1%). Laminae have discordant avenues that have remobilized sphalerite, galena, calcite, quartz. High grade. ~30% galena, ~10-15% sphalerite. »											
« 137.20- 137.90 Laminated dark grey mudstone, with intermittant zones of sphalerite and galena stringers, rounded laminated limestone inclusions. ~5% of the laminae are enriched with pyrite. »											
« 137.90- 141.10 Light grey mudstone, galena stringers, ~10%. Galena is coarse-grained and is likely later stage mineralization. Yellowish colour is associated with sphalerite enrichments, up to 5-10%, however not as pervasive as galena stringers. Majority of mineralization is conformable to S0. Calcite veining concentrates in some areas, not uniformly distributed. »											
« 141.10- 143.80 Medium to dark-grey laminated mudstone, numerous white calcite and qt, conformable veins 2-10mm thick. Laminae are wavy and often brutally failed. Pyrite pseudobeds are common. Rounded, and laminated limestone clasts often distort laminae. Later stage qt-cal vein swarms are discordant. »											
« 143.80- 144.20 Basal limestone with calcite and quartz veining (up to 50%). »											
144.20	221.00	CCMS	635138	144.20	144.80	0.60	0.01	0.01	1.00	5.00	2.00
CCMS – Calcareous Mudstone			635139	144.80	145.70	0.90	0.01	0.01	1.00	5.00	2.00
			635140	145.70	146.50	0.80	0.01	0.01	1.00	5.00	2.00
			635141	145.70	146.50	0.80	0.01	0.01	1.00	5.00	2.00
Massive, calcareous, carbonaceous, dark grey mudstone. Most of the member is massive, but rare poorly defined bedding and pyrite-calcite micro-concretions are present. Most diagnostic structures are feathery calcite beds (=thin calcite-cemented concretions, many of them contain pyrite cores) and calcite pseudo-beds (= fibrous calcite vein parallel to bedding).											

Selwyn Project Diamond Drill Log

Hole Number:
XYC-239

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		« lm ca 5.00-10.00mm », « nodules py -3.00% 2.00-20.00mm » « 144.20- 221.00 Some common characteristics of this unit include: Pyrite pseudobeds 2-40mm thick. Thin (<1mm) conformable wispy calcite veinlets. Wiggly, broken and discontinuous qt-calcite veins, randomly oriented. Varying amounts of calcareous content throughout, but in general quite low. Pyritic laminae can be broken up and moved randomly about. » « 144.20- 145.70 Much of the gouge is cemented by calcite. Flt »« Flt gg 15%»« Flt bx 10%»« Brco 75%» « 149.40- 149.70 Flt »« Flt gg 15%»« Flt bx 60%»« Brco 25%» « 152.50- 161.30 Region of increased calcite veining (up to 10%) and related fracturing and faulting. » « @ 162.00 S0 defined by pyritic laminae. S0 tca 59° » « 167.50- 168.10 Limestone, light grey and apparently bioturbated weakly. Pyrite and calcite veins increase near base. » « @ 172.40 S0 defined by wispy calcite. S0 tca 40° » « 179.20- 179.40 Flt »« Flt gg 80%»« Flt bx 20%» « @ 194.00 S0 defined by laminae. S0 tca 55° » « 206.00- 216.00 Flt »« Flt gg 30%»« Flt bx 35%»« Brco 35%» « 217.40- 221.00 Flt »« Flt gg 10%»« Flt bx 40%»« Brco 50%»									



Hole Number:
XYC-239

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		« 200.00- 221.00 The final 20m of the hole is highly faulted and fractured with abundant gouge developed, and increases in calcite content around some gouge zones. Rock type is very typical of ccms unit, relatively more fractured near base. »									
221.00	221.00	EOH									

Diamond Drill Log

Comprehensive Report for Hole:

XYC-238

Hole No.: XYC-238	Depth: 332.00 m	Horizontal Length: 0.00 m	Project: 1710
Location Data:			
Property:	Selwyn Project	Claim Name:	X 43
Mining District:	Selwyn Basin	Grant Number:	Y 64676
Province/Territory:	Yukon		
UTM Co-Ordinates & Altitude of Drill Hole Collar:			
UTM Easting:	487925.74 m	True Azimuth:	75.0 °
UTM Northing:	6926795.83 m	Hole Angle:	-50.0 °
Elevation (m):	1491.56 m	NTS Name:	Placer Creek
		NTS Number:	105L06
Grid Co-Ordinates of Drill Hole Collar:			
Grid Easting (m):	0.00 m	Grid Name:	HP 06
Grid Northing (m):	0.00 m	Grid Type:	100m
Grid Azimuth:	135.0 °		
Dimond Drilling Contract:			
Drilled By:	CY-02	Date Drilling Start:	10/25/2010
		Date Finish:	11/03/2010
Diamond Drill Core:			
Logged By:	Kate Cameron / Graham	Date Logging Start:	11/03/2010
		Date Finish:	
Legend for Core Logging Codes: PAX			
Core Size:	NQ	Cemented:	Yes
Casing Depth:	6.70 m	Casing Pulled:	Yes
Water Depth:	0.00 m	Overburden Depth:	6.70 m
Level:	Section:	Drift:	

Selwyn Project

Diamond Drill Log

Survey Data for Hole

XYC-238

Hole Comments:

Tue, Oct 26 --- Yesterday moved to target #35a. 6m of casing down. Their water supply dried up last night and they had to dig a bigger sump, all is ready for coring today.

=====

Wed, Oct 27 ---At 116 meters in deep footwall as expected; unit is either wavy banded limestone or transition formation - the core was examined in difficult conditions this morning - will revise when examined more thoroughly. Drilling is going well

=====

Thu, Oct 28 --- Total depth 242m in CCMS; 126 meters over the past day. TRAN-CCMS contact at 130.5m, defined by a 10-15cm partially healed fault. No major fault has been intersected yet, this has all been easily drilled, competent rock.

=====

Fri, Oct 29 --- Total depth 299m in a badly faulted zone, likely in CCMS. This hole was in CCMS from 130.5m to 260m, where it changed into a laminated and brecciated limestone, possibly transition formation, then back into CCMS at 286m. Fault starts at 292.5m

=====

Sat, Oct 30 --- Total depth 331m. We have hit the major fault. It started at 292.5m and we are still in it. 60% fault gouge; 40% broken, black, unidentifiable core. Slow drilling

=====

Sun, Oct 31 --- "They have cemented the bad fault. Rods had to be reamed all the way out of the fault yesterday, which was a slow process. Cement was pumped down yesterday afternoon/evening, they will wait until mid-day when it is set and start drilling again."

=====

Mon, Nov 01 --- "Total depth is still at 332m. They are still reaming to get to bottom, the rods are free but water pressure is high. The cementing partially worked, but did not make it all the way to bottom due to cave in."

=====

Tue, Nov 02 --- "No progress yet, still fighting with the fault, rods are on the way back down the hole right now."

=====

Wed, Nov 03 --- "The hole was lost yesterday when heading back down the hole and the rods veered off and started drilling a new hole. This caused the core barrel, with tube inside, to break off at the locking coupler. It was decided there was no way to continue drilling this same hole. A final decision will be made once David is in camp this morning, but preliminary talks last night left us with the idea of moving this rig to Don Zone today, and avoid struggling with the large fault we are inevitably going hit again from this set up."

=====

Thu, Nov 04 ---The hole was shutdown yesterday and they packed up and readied for a move. On standby last night and this morning, as we wait for NL-03 to get out of the way in XY West. They are spending the morning moving hoseline. We will move this rig to setup for target #68, on the same pad as targets #52, #53 and #64. (see update in collar setups tab - setup D109). Hopefully we can get a good start on this move today.

Selwyn Project

Diamond Drill Log

Survey Data for Hole

XYC-238

Selwyn Chihong Mining Ltd.#700-509 Richards Street
Vancouver, British Columbia
Canada V6B 2Z6

<i>Depth</i>	<i>Dip</i>	<i>Azimuth</i>
0.00	-50.0	75.0
59.00	-49.3	73.8
107.00	-50.0	75.6
152.00	-49.5	73.9
200.00	-50.1	74.6
251.00	-50.4	75.9

Selwyn Project Diamond Drill Log

Hole Number:
XYC-238

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
0.00	6.70	OVBR									
6.70	130.60	CLST									
<i>CLST – Cambrian Limestone</i> <i>Consists of 2 units. The first unit, Wavy Banded Limestone Formation, is divided into two informal members, based on the amount of argillaceous material in some beds. Both members display well-banded limestone. The upper member consists of intercalated light grey siliceous micrite and grey to tan laminated calcareous mudstone beds, displaying a chain-link structure. It appears wavy because of variable bedding thickness. Bedding is in general thinner than the bedding in the lower member, with micrite beds ranging from 1 to 5 cm thick, and showing rapid lateral variation. The lower member consists of intercalated microspar and micrite, and shows even bedding.</i> <i>The second unit, Massive Limestone Formation, consists of massive grey, micritic siliceous limestone. « lt gra , lm microspar 5.00-40.00cm », « lm micrite 1.00-5.00cm », « gra to lt bro , calcareous mdst 5.00-30.00mm »</i> <i>« 6.70- 130.50 Wavy banded limestone. Mottled light grey limestone with boudenaged (chain link) appearance. Moderately strong HCl reaction. »</i> <i>< @ 20.50 S0 in an area of planar parallel light grey laminae. S0 tca 25° ></i> <i>< @ 42.70 S0 in an area of planar parallel light grey laminae. S0 tca 30° ></i> <i>« 47.50- 54.00 Increased calcite veining. »</i> <i>< @ 67.60 S0 in an area of planar parallel light grey laminae. S0 tca 15° ></i> <i>< @ 77.10 S0 in an area of planar parallel light grey laminae. S0 tca 25° ></i> <i>< @ 105.40 S0 in an area of planar parallel light grey laminae. S0 tca 25° ></i> <i>< @ 122.20 S0 in an area of planar parallel light grey laminae. S0 tca 40° ></i> <i>« 125.30- 130.50 Unit gradually darkens as more argillicious material is incorporated. »</i>											

Selwyn Project Diamond Drill Log

Hole Number:
XYC-238

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		« 130.50- 130.60 Mostly healed/reconstituted. Flt »« Flt gg 80%»« Flt bx 20%»									
130.60	259.20	CCMS									
CCMS – Calcareous Mudstone											
Massive, calcareous, carbonaceous, dark grey mudstone. Most of the member is massive, but rare poorly defined bedding and pyrite-calcite micro-concretions are present. Most diagnostic structures are feathery calcite beds (=thin calcite-cemented concretions, many of them contain pyrite cores) and calcite pseudo-beds (= fibrous calcite vein parallel to bedding). « lm ca 5.00-10.00mm », « nodules py -3.00% 2.00-20.00mm » « 130.60- 259.20 Monotonous. Typical, except for abundant calcite stringers and veins. Whispy pyrite and calcite. Up to 2% disseminated pyrite throughout, concentrating with qt-cal. Limestone layers typically 15-30cm thick. Description of unit: Laminated dark grey mudstone, intercalated with calcite. Variable disseminated pyrite up to 2%. Specular and framboidal pyrite +/- cal/qt. Calcite/qt vein swarms may brecciate host rock in some cases. S0 is largely defined by laminae 1-7mm thick and stand out with feathery calcite beds. Layers have variable pyrite concentrations.» ‹ @ 150.70 S0 in whispy planar parallel calcite veins. S0 tca 20° › ‹ @ 188.20 S0 in parallel planar whispy calcite and disseminated pyrite. S0 tca 10° › ‹ @ 212.20 S0 in planar parallel whispy calcite. S0 tca 20° › ‹ @ 212.40 Veining set. Planar parallel 0.5mm to 3mm calcite veins. tca 70° › ‹ @ 221.70 S0 defined by laminae/ depositional banding. S0 tca 56° › ‹ @ 224.50 S0 defined by laminae/depositional banding. S0 tca 45° › ‹ @ 238.60 S0 defined by laminae/depositional banding. S0 tca 70° ›											

Selwyn Project Diamond Drill Log

Hole Number:
XYC-238

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		< @ 245.90 S0 defined by laminae/depositional banding. S0 tca 65° > < @ 255.10 S0 defined by laminae/depositional banding. S0 tca 25° >									
259.20	292.40	TRAN									
TRAN – Transition Formation											
Consists of laminated tan mudstone and minor intercalated light grey limestone. « lm mdst 1.00-10.00mm » « 259.20- 292.40 Light to medium grey muddy limestone to calcic mudstone. Calcareous content is less than in the wavy banded limestone; however the texture of the fabric is wavy with abundant angular to sub-rounded limestone clasts that cause a pseudo 'chain-link' appearance. Laminae are 1-5mm thick alternating between light-grey, brownish-grey, and grey laminae. Angular to sub-rounded clasts of limestone concentrate in some layers and may take on mosaic pattern near depositional bases- indicated scouring of deposited limestone and ecorporation within wavy texture. Chert layers are minor but are light-grey- 7-13mm thick. Veining consists of recrystallized qt and carbonate. Very coarse grained when veining exceeds 5cm thick, fairly systematic veining that tends to cut orthogonal to S0. »											
< @ 262.80 S0 defined by laminae and chert band. S0 tca 42° > < @ 264.20 S0 defined by laminae. S0 tca 22° > < @ 266.80 S0 defined by elongated limestone clasts- very low angle cross bedding. S0 tca 0° > < @ 268.30 S0 defined by laminae. S0 tca 0° > < @ 277.30 S0 defined by laminae. S0 tca 0° > « 281.80- 283.30 Mud intruded limestone. Mosaic brecciation of light grey limestone with dark grey-black mud matrix. ~90% limestone and ~10% mud. »											
< @ 285.10 S0 defined by laminae. S0 tca 15° > « 283.30- 291.50 Cross-bedded TRAN with medium grey laminated calcareous											

Page: 4

Diamond Drill Log

Comprehensive Report for Hole:

XYC-237

Hole No.: XYC-237	Depth: 404.30 m	Horizontal Length: 0.00 m	Project: 1710
Location Data:			
Property:	Selwyn Project	Claim Name:	X16
Mining District:	Selwyn Basin	Grant Number:	Y 64541
Province/Territory:	Yukon		
UTM Co-Ordinates & Altitude of Drill Hole Collar:			
UTM Easting:	487502.36 m	True Azimuth:	137.0 °
UTM Northing:	6927241.71 m	Hole Angle:	-86.0 °
Elevation (m):	1486.14 m	NTS Name:	Placer Creek
		NTS Number:	105L06
Grid Co-Ordinates of Drill Hole Collar:			
Grid Easting (m):	0.00 m	Grid Name:	HP 06
Grid Northing (m):	0.00 m	Grid Type:	100m
Grid Azimuth:	197.0 °		
Dimond Drilling Contract:			
Drilled By:	NL-02	Date Drilling Start:	10/23/2010
		Date Finish:	10/29/2010
Diamond Drill Core:			
Logged By:	Kate Cameron/Greg Stone	Date Logging Start:	1/17/2011
		Date Finish:	1/21/2010
Legend for Core Logging Codes: PAX			
Core Size:	NQ	Cemented:	Yes
Casing Depth:	10.40 m	Casing Pulled:	
Water Depth:	0.00 m	Overburden Depth:	10.40 m
Level:	Section:	Drift:	

Selwyn Project

Diamond Drill Log

Survey Data for Hole

XYC-237

Hole Comments:

Sun, Oct 24 --- Successfully removed NQ rod string yesterday after some difficulty, and turned the drill to XYC-237 (Setup #63 on same pad). 9.1 meters of casing; total depth 23.3 meters Rock is broken-up FLMD.

=====

Mon, Oct 25 ---Drilling in broken-up USMS at 95.3 meters. FLMD-USMS contact at 35 meters. Rods stuck last night at 76 meters; pulled rods and changed bit.

=====

Tue, Oct 26 --- Currently at 185.3 meters. The drilling going fairly well with only minor mechanical problems and some briefly stuck rods yesterday. The core, however, is quite odd: We were in definite USMS to 125.8 meters where we hit a 1 meter fault. Following the fault we have FLMD to 156.5 meters, where we hit a 5 meter fault. Following this we have dark grey siliceous mudstone to current depth. The unit may be USMS, but if so, it is not typical. Chert banding is common throughout, suggesting USMS, but similar carbonate banding and carbonate concretions are totally absent. There are also very few veins of any type, and the rock has a general appearance somewhat suggestive of BSSM. The plot thickens.

=====

Wed, Oct 27 ---Hit ACTM at 215.3 to 235.8 meters, now in probable CCMS. I want to see a little more of the core, as it was somewhat unusual footwall, but we may begin shutting the hole down this afternoon.

=====

Thu, Oct 28 --- In certain CCMS at 323.3 meters. Drilling going quite well. Will test footwall to TRAN as requested.

=====

Fri, Oct 29 --- Shut down this morning at 404.3 meters in Transition Formation. The TRAN - CCMS/PSMS (tbd) contact is at approxiamtely 381 meters. We will attempt to go back onto XYC-220 to retrieve cut the core barrel and retrieve the NQ rods, but it could be very difficult given the hole condition and the deteriorating condition of the bank.

<i>Depth</i>	<i>Dip</i>	<i>Azimuth</i>
0.00	-86.0	137.0
50.00	-85.4	140.1
100.00	-84.6	143.1
150.00	-84.5	146.0
200.00	-85.4	147.3
250.00	-84.5	153.3
300.00	-86.3	151.2
350.00	-85.1	161.3
400.00	-85.5	162.7

Selwyn Project Diamond Drill Log

Hole Number:
XYC-237

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
0.00	10.40	OVBR									
10.40	33.00	FLMD <i>FLMD – Flaggy Mudstone Formation</i> <i>Dark grey mudstone in the upper portions of the unit grading into light grey mudstone to siltstone. Contains abundant wispy bioturbation which ranges from randomly-oriented at the top of the unit to bedding-parallel throughout the majority of the unit. Darker upper section has a strong fetid odour along broken surfaces. « btrb 0.10-2.00cm », « cg xtl crns ca 1.00-5.00% 5.00-150.00cm », « crns py 1.00-5.00% 0.10-0.50mm »,</i> <i>« 10.40- 33.00 Broken zone. »</i>									
33.00	104.00	USMS <i>USMS – Upper Siliceous Mudstone</i> <i>Consists of interlaminated dark grey to black mudstone and light to medium grey chert. Regionally, a 1m thick graptolite zone occurs 15m below the top of the upper unit, this is usable as a horizon. The USMS is divided into 3 units. The Lower Unit contains abundant limestone concretions and Galena and sphalerite micro-concretions occur locally near the base of this unit. « gra , lm chrt -20.00% », « cg xtl sph crns ca 5.00-20.00cm », « bed chrt 10.00-15.00% »,</i> <i>« 33.00- 104.00 Very broken up. Calcite is stained yellow. Limestone concretions have some yellow staining as well. Mangled chert bands. »</i> <i>« 33.00- 35.30 Broken zone. »</i> <i>« 35.30- 81.70 Fault zone. FLT »« Flt gg 15%»« Flt bx 30%»« Brco 25%»</i>									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-237

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
104.00	133.80	FLT									
«104.00- 133.80 Both USMS and FLMD identifiable throughout fault. FLT »« Flt gg 10%»« Flt bx 40%»« Brco 30%»											
133.80	161.80	FLMD									
FLMD – Flaggy Mudstone Formation											
Dark grey mudstone in the upper portions of the unit grading into light grey mudstone to siltstone. Contains abundant wispy bioturbation which ranges from randomly-oriented at the top of the unit to bedding-parallel throughout the majority of the unit. Darker upper section has a strong fetid odour along broken surfaces. « btrb 0.10-2.00cm », « cg xtl crns ca 1.00-5.00% 5.00-150.00cm », « crns py 1.00-5.00% 0.10-0.50mm »,											
◁ @ 142.50 S0 defined by compositional differences in bioturbated zone. S0 tca 42° ▷											
◁ @ 151.70 S0 defined by compositional differences in bioturbated zone. S0 tca 49° ▷											
« 156.50- 157.30 FLT »« Flt gg 20%»« Flt bx 80%»											
161.80	213.00	USMS	628601	211.00	212.00	1.00					
USMS – Upper Siliceous Mudstone			628602	212.00	213.00	1.00					
Consists of interlaminated dark grey to black mudstone and light to medium grey chert. Regionally, a 1m thick graptolite zone occurs 15m below the top of the upper unit, this is usable as a horizon. The USMS is divided into 3 units. The Lower Unit contains abundant limestone concretions and Galena and sphalerite micro-concretions occur locally near the base of this unit. « gra , lm chrt -20.00% », « cg xtl sph crns ca 5.00-20.00cm », « bed chrt 10.00-15.00% »,											
◁ @ 171.80 S0 defined by chert bands. S0 tca 45° ▷											
◁ @ 182.20 S0 defined by chert bands. S0 tca 41° ▷											

Selwyn Project Diamond Drill Log

Hole Number:
XYC-237

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
< @ 189.60 S0 defined by chert bands. S0 tca 36° > « 192.80- 202.60 FLT »« Flt gg 20%»« Flt bx 40%»« Brco 20%» < @ 206.80 Patchy galena up to 3mm thick in two veins. No other associated mineralization. > < @ 211.00 S0 defined by chert bands. S0 tca 35° >											
213.00	235.00	ACTM	628603	213.00	214.00	1.00					
ACTM – Active Member			628604	214.00	215.50	1.50					
The ACTM consists of a repetitive, possibly rhythmic, sequence of intercalated carbonaceous mudstone, cherty mudstone, chert and limestone and locally contains economically significant Zn and Pb sulphides (see bold marked facies), mainly in its sections with well developed lamination. Because of its heterogeneity, the member is distinctive and easily identified. ===== The ACTM has 8 different facies: ===== - GREY CHERT FACIES: Consists of laminated medium light grey to medium dark grey chert. Mineralization: 95-99% quartz and up to 5% secondary calcite. - WHITISH GREY ZN-PB MUDSTONE FACIES: Is a laminated cherty rock containing up to 70% sulphides. Mineralization: quartz, sphalerite and galena are the major minerals with only minor amounts of pyrite and locally calcite. Sedimentary diagenetic structures are common and well displayed in the facies, such as: lamination, pseudo-beds, calcite nodules & limestone nodules and abundant water escape structures. Most obvious structure in facies is cross-cutting veins containing massive sphalerite and galena with minor pyrite. They range in width from 0.5 to 10mm.			628605	215.50	216.50	1.00					
			628606	216.50	217.10	0.60					
			628607	217.10	217.60	0.50					
			628608	217.60	218.00	0.40					
			628609	218.00	219.10	1.10					
			628610	219.10	220.40	1.30					
			628611	219.10	220.40	1.30					
			628612	220.40	221.00	0.60					
			628613	221.00	222.50	1.50					
			628614	222.50	223.30	0.80					
			628615	223.30	224.40	1.10					
			628616	224.40	225.10	0.70					
			628617	225.10	226.40	1.30					
			628618	226.40	227.20	0.80					
			628619	227.20	228.70	1.50					
			628620	228.70	228.70	0.00					
			628621	228.70	229.70	1.00					
			628622	229.70	230.40	0.70					
			628623	230.40	231.90	1.50					
			628624	231.90	232.80	0.90					
			628625	232.80	234.00	1.20					
			628626	234.00	235.00	1.00					

Selwyn Project Diamond Drill Log

Hole Number:
XYC-237

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		- <i>THIN BEDDED CHERTY MUDSTONE FACIES: Consists of rhythmic intercalated laminae of chert, carbonaceous mudstone and minor micrite. This facies contains significant amounts of Zn and Pb sulphides.</i> - <i>CHERTY MUDSTONE FACIES: Consists of a greyish black monotonous siliceous, carbonaceous mudstone. It is most typically found overlying the thin bedded calcareous mudstone facies.</i> - <i>THIN BEDDED CALCAREOUS MUDSTONE FACIES: Consists of laminated carbonaceous mudstone containing 20-40% calcite, 40-55% quartz and 10-20% muscovite. Sulphides occur in laminae. In the XY area it is usually the lowest facies in the section to contain laminated sulphides.</i> - <i>CALCAREOUS MUDSTONE FACIES: Consists of grey to greyish black monotonous, calcareous siliceous carbonaceous mudstone. There are no feathery calcite beds or pyrite-calcite blebs in the facies, making it easily distinguishable from the CCMS.</i> - <i>GRADED LIMESTONE FACIES: Is a laminated argillaceous limestone with intercalated carbonaceous limestone laminae. The main rock type in the facies is laminated limestone with laminae up to 0.1-7mm thick.</i> - <i>LIGHT GREY BASAL LIMESTONE FACIES - LGLS: Consists of laminated argillaceous limestone. In the Anniv area it marks the end of the ACTM. It's not always present in the stratigraphy.</i> - <i>BASAL FACIES: This is a highly contorted and locally foliated carbonaceous mudstone. Unlike the other facies it is not repeated higher in the member. It appears locally to contain the slip zone of a major slump. The facies has only been observed in the YX area. It is 0.1-2m thick. The facies consists of massive carbonaceous siliceous mudstone with lenses and laminae of contorted, slightly carbonaceous chert.</i>									

Selwyn Project

Diamond Drill Log

Hole Number:
XYC-237

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
« 213.00- 217.10 Silicious mudstone with weak fine grained sphalerite laminations. Patchy coarse grained galena veins at <1%. Limestone clasts up to 15cm. »											
« 217.10- 217.60 Coarse grained limestone with no visible mineralization. »											
« 217.60- 219.10 Silicious mudstone moderately developed sphalerite laminations. Sparse coarse grained galena veins. »											
« 219.10- 220.40 Light grey medium grained limestone. 20% calcite veins. No visible mineralization. »											
« 220.40- 224.40 Dark grey silicious mudstone. Patchy weak sphalerite/galena laminations. »											
« 224.40- 225.10 Light grey limestone. No visible mineralization. »											
« 225.10- 230.50 Medium grey calcareous mudstone. Moderately developed sphalerite/galena laminations. Few coarse grained galena veins. »											
« 230.50- 232.80 Light grey basal limestone. Sphalerite and galena present in calcite veins. »											
« 232.80- 235.00 Calcareous mudstone and light grey limestone in very broken/faulted zone. Zn + Pb mineralization. »											
235.00	238.80	FLT	628627	235.00	236.00	1.00					
«235.00- 238.80 FLT »« Flt gg 15%»« Flt bx 60%»« Brco 15%»			628628	236.00	237.00	1.00					
			628629	237.00	237.00	0.00					
238.80	377.80	CCMS									
CCMS – Calcareous Mudstone											
Massive, calcareous, carbonaceous, dark grey mudstone. Most of the member is massive, but rare poorly defined bedding and pyrite-calcite micro-concretions are present. Most diagnostic structures are feathery calcite beds (=thin											

Selwyn Project Diamond Drill Log

Hole Number:
XYC-237

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		calcite-cemented concretions, many of them contain pyrite cores) and calcite pseudo-beds (= fibrous calcite vein parallel to bedding). « lm ca 5.00-10.00mm », « nodules py -3.00% 2.00-20.00mm », « 238.80- 377.80 Core is very broken throughout. Some unusual features in this core (possibly BSSM): wormy calcite and chert bands- very rare, only seen in one spot. Moderately calcareous. Medium to dark grey- lighter than typical 'CCMS'. » « 263.10- 276.60 FLT »« Flt gg 20%»« Flt bx 50%»« Brco 15%» « @ 291.50 S0 defined by feathery calcite/pyrite beds. S0 tca 55° » « 292.40- 295.70 FLT »« Flt gg 10%»« Flt bx 70%»« Brco 20%» « @ 305.50 S0 defined by pyrite pseudobeds. S0 tca 61° » « 306.40- 333.50 10-15% calcite veins. From hairline to 30cm thick at varying orientations. » « @ 359.40 S0 defined by feathery calcite beds. S0 tca 55° » « 376.40- 377.80 30% quartz/calcite veins- possibly healed fault? »									
377.80	404.30	TRAN									
		TRAN – Transition Formation Consists of laminated tan mudstone and minor intercalated light grey limestone. « lm mdst 1.00-10.00mm », « 377.80- 404.30 Laminated weakly calcareous mudstone. Some sections are massive with no laminations. 1-5% pyrite blebs parallel to bedding. »									



Hole Number:
XYC-237

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

Page: 7

Diamond Drill Log

Comprehensive Report for Hole:

XYC-236

Hole No.: XYC-236	Depth: 177.60 m	Horizontal Length: 0.00 m	Project: 1710
Location Data:			
Property:	Selwyn Project	Claim Name:	X 16
Mining District:	Selwyn Basin	Grant Number:	Y 64541
Province/Territory:	Yukon		
UTM Co-Ordinates & Altitude of Drill Hole Collar:			
UTM Easting:	489100.01 m	True Azimuth:	180.0 °
UTM Northing:	6926149.14 m	Hole Angle:	-86.0 °
Elevation (m):	1608.24 m	NTS Name:	Placer Creek
		NTS Number:	105L06
Grid Co-Ordinates of Drill Hole Collar:			
Grid Easting (m):	0.00 m	Grid Name:	HP 06
Grid Northing (m):	0.00 m	Grid Type:	100m
Grid Azimuth:	240.0 °		
Dimond Drilling Contract:			
Drilled By:	CY-01	Date Drilling Start:	10/22/2010
		Date Finish:	10/25/2010
Diamond Drill Core:			
Logged By:	Kate Cameron / Graham	Date Logging Start:	11/01/2010
		Date Finish:	
Legend for Core Logging Codes: PAX			
Core Size:	NQ	Cemented:	Yes
Casing Depth:	4.90 m	Casing Pulled:	Yes
Water Depth:	0.00 m	Overburden Depth:	4.90 m
Level:			
Section:		Drift:	

Selwyn Project

Diamond Drill Log

Survey Data for Hole

XYC-236

Hole Comments:

Sat, Oct 23 --- Shut down at 187.4m in CCMS. Changed to target #55. XYC-236 is at 23m in broken USMS. 6.1m of casing

=====

Sun, Oct 24 --- Very broken, faulted USMS to 74 meters, where we hit ACTM. Primarily low to medium grade, sporadic mineralization and quite broken up. Now at 110 meters after two excellent shifts; still drilling but may be crossing over to CCMS. Could shut down today.

=====

Mon, Oct 25 ---"Total depth 170m in CCMS. ACTM was from 74-112m. Going to drill for a couple more hours while CY-02 is moved. "

<i>Depth</i>	<i>Dip</i>	<i>Azimuth</i>
0.00	-86.0	180.0
50.00	-85.5	177.5
113.00	-84.3	187.4
155.00	-82.7	190.8
177.00	-83.0	188.0

Selwyn Project Diamond Drill Log

Hole Number:
XYC-236

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
0.00	4.90	OVBR									
4.90	71.40	USMS	634051	59.40	59.90	0.50	0.01	0.01	1.00	5.00	2.00
USMS – Upper Siliceous Mudstone <i>Consists of interlaminated dark grey to black mudstone and light to medium grey chert. Regionally, a 1m thick graptolite zone occurs 15m below the top of the upper unit, this is usable as a horizon. The USMS is divided into 3 units. The Lower Unit contains abundant limestone concretions and Galena and sphalerite micro-concretions occur locally near the base of this unit. « gra , lm chrt -20.00% », « cg xtl sph crns ca 5.00-20.00cm », « bed chrt 10.00-15.00% »</i> <i>« 4.90- 71.40 Non-typical USMS. Looks almost like CCMS. Few chert bands. Black, silicious, monotonous. Bands of disseminated pyrite. Few calcite veins, which are ~0.5cm, fractured but not wormy. Pyrite also in blebs but not elongate. Carbonaceous. Fain near-planar lamination in some zones. »</i> <i>« 4.90- 49.60 Near surface breakage or just a generally busted up zone. Flt »« Flt gg 10%»« Flt bx 10%»« Brco 20%»</i> <i>« 55.60- 71.40 Dark-grey to black, poorly laminated silicious mudstone. ~2-3% quartz-calcite veins, conformable to S0, typically 3-5mm thick. Numerous machine breaks, due to highly fractured nature of rock. Bioturbated with laminated limestone commonly in 20cm intervals. Weakly mineralized. »</i> <i>« 64.40- 67.30 Flt »« Flt gg 5%»« Flt bx 70%»« Brco 25%»</i>			634052	59.90	60.40	0.50	0.01	0.01	1.00	5.00	2.00
			634053	60.40	61.50	1.10	0.01	0.12	1.00	5.00	0.08
			634054	61.50	62.70	1.20	0.01	0.11	1.00	5.00	0.09
			634055	62.70	64.30	1.60	0.01	0.25	1.00	5.00	0.04
			634056	64.30	65.20	0.90	0.16	0.28	1.00	5.00	0.57
			634057	65.20	66.50	1.30	0.05	0.62	1.00	20.00	0.08
			634058	66.50	67.40	0.90	0.01	0.20	1.00	5.00	0.05
			634059	67.40	67.70	0.30	0.01	0.17	1.00	5.00	0.06
			634060	67.70	68.00	0.30	0.08	0.64	1.00	20.00	0.13
			634061	67.70	68.00	0.30	0.31	0.85	1.00	20.00	0.36
			634062	68.00	69.30	1.30	0.08	0.16	1.00	5.00	0.50
			634063	69.30	70.70	1.40	0.03	0.40	1.00	10.00	0.08
			634064	70.70	71.40	0.70	0.01	0.22	1.00	5.00	0.05
71.40	112.30	ACTM	634065	71.40	71.60	0.20	0.01	0.01	1.00	5.00	2.00
ACTM – Active Member <i>The ACTM consists of a repetitive, possibly rhythmic, sequence of intercalated carbonaceous mudstone, cherty mudstone, chert and limestone and locally contains economically significant Zn and Pb sulphides (see bold marked facies), mainly in its sections with well developed lamination. Because of its heterogeneity, the member is distinctive and easily identified.</i>			634066	71.60	72.30	0.70	0.03	0.16	2.00	5.00	0.19
			634067	72.30	73.10	0.80	0.12	0.06	1.00	5.00	2.00
			634068	73.10	73.50	0.40	0.55	1.06	1.00	30.00	0.52
			634069	73.50	74.10	0.60	1.11	5.44	1.00	180.00	0.20
			634070	74.10	74.10	0.00	0.01	0.01	1.00	5.00	2.00
			634071	74.10	75.00	0.90	2.69	5.16	3.00	170.00	0.52
			634072	75.00	75.50	0.50	0.28	2.78	1.00	100.00	0.10

Selwyn Project Diamond Drill Log

Hole Number:
XYC-236

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
=====			634073	75.50	76.10	0.60	0.89	3.20	1.00	100.00	0.28
			634074	76.10	76.60	0.50	0.05	0.27	1.00	5.00	0.19
The ACTM has 8 different facies:			634075	76.60	77.40	0.80	1.66	13.21	3.00	410.00	0.13
=====			634076	77.40	77.80	0.40	0.47	1.29	1.00	40.00	0.36
			634077	77.80	78.30	0.50	0.01	0.24	1.00	5.00	0.04
- GREY CHERT FACIES: Consists of laminated medium light grey to medium dark grey chert. Mineralization: 95-99% quartz and up to 5% secondary calcite.			634078	78.30	79.00	0.70	0.01	0.11	1.00	5.00	0.09
			634079	79.00	80.20	1.20	0.03	0.98	1.00	30.00	0.03
			634080	80.20	80.20	0.00	1.37	2.99	18.00	180.00	0.46
- WHITISH GREY ZN-PB MUDSTONE FACIES: Is a laminated cherty rock containing up to 70% sulphides. Mineralization: quartz, sphalerite and galena are the major minerals with only minor amounts of pyrite and locally calcite. Sedimentary diagenetic structures are common and well displayed in the facies, such as: lamination, pseudo-beds, calcite nodules & limestone nodules and abundant water escape structures. Most obvious structure in facies is cross-cutting veins containing massive sphalerite and galena with minor pyrite. They range in width from 0.5 to 10mm.			634081	80.20	80.60	0.40	0.02	0.50	1.00	10.00	0.04
			634082	80.60	81.30	0.70	0.64	5.77	1.00	150.00	0.11
			634083	81.30	82.20	0.90	0.60	4.68	1.00	140.00	0.13
			634084	82.20	83.90	1.70	0.68	3.78	1.00	100.00	0.18
			634085	83.90	84.90	1.00	0.01	0.31	1.00	5.00	0.03
			634086	84.90	86.10	1.20	0.01	0.01	1.00	5.00	1.00
			634087	86.10	87.20	1.10	0.04	0.23	1.00	5.00	0.17
			634088	87.20	88.30	1.10	0.01	0.04	1.00	5.00	0.25
			634089	88.30	89.60	1.30	0.21	1.31	1.00	30.00	0.16
- THIN BEDDED CHERTY MUDSTONE FACIES: Consists of rhythmic intercalated laminae of chert, carbonaceous mudstone and minor micrite. This facies contains significant amounts of Zn and Pb sulphides.			634090	89.60	90.10	0.50	0.16	0.31	1.00	5.00	0.52
			634091	89.60	90.10	0.50	0.16	1.15	1.00	20.00	0.14
			634092	90.10	90.70	0.60	0.13	0.05	1.00	5.00	2.60
			634093	90.70	91.30	0.60	0.01	0.01	1.00	5.00	2.00
- CHERTY MUDSTONE FACIES: Consists of a greyish black monotonous siliceous, carbonaceous mudstone. It is most typically found overlying the thin bedded calcareous mudstone facies.			634094	91.30	92.90	1.60	0.76	3.10	1.00	90.00	0.25
			634095	92.90	93.70	0.80	1.40	4.04	1.00	110.00	0.35
			634096	93.70	94.30	0.60	2.39	6.94	1.00	180.00	0.34
			634097	94.30	95.20	0.90	0.76	3.94	1.00	100.00	0.19
- THIN BEDDED CALCAREOUS MUDSTONE FACIES: Consists of laminated carbonaceous mudstone containing 20-40% calcite, 40-55% quartz and 10-20% muscovite. Sulphides occur in laminae. In the XY area it is usually the lowest facies in the section to contain laminated sulphides.			634098	95.20	95.70	0.50	3.50	15.54	3.00	500.00	0.23
			634099	95.70	96.10	0.40	1.45	6.50	1.00	170.00	0.22
			634100	96.10	96.10	0.00	0.01	0.05	1.00	5.00	0.20
			634101	96.10	97.00	0.90	1.35	3.29	1.00	80.00	0.41
			634102	97.00	97.40	0.40	0.16	0.01	1.00	5.00	32.00
- CALCAREOUS MUDSTONE FACIES: Consists of grey to greyish black monotonous, calcareous siliceous carbonaceous mudstone. There are no feathery calcite beds or pyrite-calcite blebs in the facies, making it easily distinguishable from			634103	97.40	98.50	1.10	0.61	0.24	1.00	5.00	2.54
			634104	98.50	98.90	0.40	0.37	0.40	1.00	5.00	0.93
			634105	98.90	99.30	0.40	0.20	0.13	1.00	5.00	1.54

Selwyn Project Diamond Drill Log

Hole Number:
XYC-236

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
the CCMS. - <i>GRADED LIMESTONE FACIES: Is a laminated argillaceous limestone with intercalated carbonaceous limestone laminae. The main rock type in the facies is laminated limestone with laminae up to 0.1-7mm thick.</i> - <i>LIGHT GREY BASAL LIMESTONE FACIES - LGLS: Consists of laminated argillaceous limestone. In the Anniv area it marks the end of the ACTM. It's not always present in the stratigraphy.</i> - <i>BASAL FACIES: This is a highly contorted and locally foliated carbonaceous mudstone. Unlike the other facies it is not repeated higher in the member. It appears locally to contain the slip zone of a major slump. The facies has only been observed in the YX area. It is 0.1-2m thick. The facies consists of massive carbonaceous siliceous mudstone with lenses and laminae of contorted, slightly carbonaceous chert.</i> « 71.40- 112.30 In general, low grade intersection. » « 71.40- 71.60 Laminated limestone, massive pyrite discordant laminae 2-10mm thick occurs often with calcite-quartz secondary mineralization. » « 71.60- 73.50 Laminated silicious mudstone, conformable quartz-calcite, deformed laminae ~2-6mm thick. ~3-4% calcite veining with recrystallized quartz. Massive pyrite blows out into blebs up to 10cm thick, often brecciated by calcite and quartz. Highly fractured, blocky ground. » « 73.50- 76.10 Light grey, slicified, mudstone, highly fractured. Minor recrystallized qt and calcite in ~5% of fractures. Massive and disseminated pyrite as described. Blocky ground, few pieces >10cm in length. » « 76.10- 76.60 No visible mineralization, slightly calcareous silicious mudstone, abundant calcite veining infills fractures (with minor quartz). Veins often brecciate the host rock.»			634106	99.30	100.00	0.70	0.19	0.72	1.00	20.00	0.26
			634107	100.00	101.00	1.00	0.04	0.47	1.00	5.00	0.09
			634108	101.00	101.80	0.80	1.00	1.16	1.00	20.00	0.86
			634109	101.80	102.10	0.30	3.31	1.28	4.00	30.00	2.59
			634110	102.10	102.10	0.00	5.93	6.67	70.00	190.00	0.89
			634111	102.10	103.20	1.10	0.22	0.94	1.00	20.00	0.23
			634112	103.20	104.20	1.00	0.09	0.17	1.00	5.00	0.53
			634113	104.20	104.60	0.40	0.10	0.38	1.00	5.00	0.26
			634114	104.60	105.30	0.70	0.33	1.48	1.00	30.00	0.22
			634115	105.30	106.10	0.80	0.06	0.33	1.00	5.00	0.18
			634116	106.10	107.00	0.90	0.78	1.52	4.00	30.00	0.51
			634117	107.00	107.50	0.50	0.30	2.53	4.00	50.00	0.12
			634118	107.50	108.50	1.00	0.15	1.16	3.00	30.00	0.13
			634119	108.50	109.10	0.60	0.09	0.87	3.00	20.00	0.10
			634120	109.10	109.40	0.30	0.14	0.04	4.00	5.00	3.50
			634121	109.10	109.40	0.30	0.30	0.03	3.00	5.00	10.00
			634122	109.40	110.00	0.60	0.01	0.01	1.00	5.00	2.00
			634123	110.00	110.60	0.60	0.62	0.24	4.00	5.00	2.58
			634124	110.60	111.50	0.90	0.01	0.01	1.00	5.00	2.00
			634125	111.50	112.30	0.80	0.03	0.01	1.00	5.00	6.00

Selwyn Project Diamond Drill Log

Hole Number:
XYC-236

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		« 76.60- 77.40 Intercalated wavy laminated metalliferous mudstone, cross-bedded. Pyritic laminae are most common sulphite laminae followed by sphalerite and galena. Deformation is ductile. » « 77.40- 92.90 Intercalated weakly calcareous, carbonaceous, slightly silicified medium grey to black mudstone with laminated calcite-quartz veined limestone. Limestone clasts throughout, rounded to sub-angular, often deforming laminae, the clasts share lithology of the limestone intervals seen through the interval. Ground is very blocky throughout, abundant faulting through entire interval. Many reconstituted gouge and breccia zones. Flt»« Flt gg 20%»« Flt bx 50%»« Brco 30%» « 92.90- 97.00 At the start of this interval the rock becomes more competent and has a much higher calcareous content. Interval consists of ~50/50 silicious and metalliferous laminated mudstone with cross-laminated limestone. Pervasive quartz-calcite veins are typically conformable to S0, secondary extensional tension gash swarms are mineralized similarly. Throughout much of the mudstone there are clasts of limestone- often stretched out along S0. » « 97.00- 104.60 Description of the previous interval applies here too, but with one modifier: Metalliferous zones are far less mineralized with base metals, typically sulphidic laminae in the mudstone are pyritic. » « 104.60- 110.60 Interlaminated to thinly interbedded graded muds and minor silts. Variable shades of grey and disseminated pyrite content distinguish the depositional bands (Typically 2-35mm thick). Specular pyrite concentrates in some laminae. ~10% calcic laminae. Many cal-qt remineralized stylolites, especially in silicious zones. Sphalerite can concentrate in some laminae; galena occurs in trace amounts as blebs 1-2mm in diameter.» « 110.60- 112.30 Basal limestone to the ACTM, barren to mineralization. Light grey contorted limestone with minor limestone clasts and calcite brecciated limestone. »									
112.30	177.60	CCMS	634126	112.30	113.00	0.70	0.06	0.43	4.00	20.00	0.14

Selwyn Project Diamond Drill Log

Hole Number:
XYC-236

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		CCMS – Calcareous Mudstone	634127	113.00	114.20	1.20	0.09	0.40	2.00	20.00	0.23
			634128	114.20	116.60	2.40	0.05	0.12	1.00	5.00	0.42
		Massive, calcareous, carbonaceous, dark grey mudstone. Most of the member is massive, but rare poorly defined bedding and pyrite-calcite micro-concretions are present. Most diagnostic structures are feathery calcite beds (=thin calcite-cemented concretions, many of them contain pyrite cores) and calcite pseudo-beds (= fibrous calcite vein parallel to bedding). « lm ca 5.00-10.00mm », « nodules py -3.00% 2.00-20.00mm » « 112.30- 177.60 Very fine-grained dark grey to black poorly laminated mudstone intercalated with calcareous laminated mudstone, planar laminae, and light-grey laminated limestone to massive limestone. Pervasive calcite veins with minor quartz throughout interval. Also thin, wispy, conformable calcite. Squiggly pyritic laminae (1-3mm thick). Much of the interval is cross-bedded at a low angle. Pseudobeds of fine grained pyrite and variable calcareous laminae are characteristic of this unit. Much of the calcareous mudstone has fine grained disseminated pyrite pervasively distributed (up to 1.5%). Calcite can remineralize stylolites and cause thickened contorted, conformable calcite veins.» « 121.40- 122.00 Interval of increased calcite-quartz veining (~50% calcite-quartz). Intrusion brecciates the host mudstone and pyrite into a reconstituted calcite-quartz-pyrite mudstone vein breccia (very angular clasts). » « @ 124.40 S0 well defined by laminae. S0 tca 46° » « @ 128.50 S0 defined by wispy planar calcite. S0 tca 48° » « 129.10- 129.20 Reconstituted gouge and breccia. Flt »« Flt gg 70%»« Flt bx 30%» « 136.80- 137.50 Flt »« Flt gg 10%»« Flt bx 40%»« Brco 50%» « @ 136.60 Elongate black chert clasts, stretched along S0. Not a									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-236

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		characteristic seen throughout interval. › « 145.30- 145.80 Limestone breccia, with mosaic-style fragmentation of calcite and quartz and limestone. » « 145.80- 149.00 Non-typical CCMS. Actually this interval looks much like USMS with slightly more contorted laminae and a higher degree of compositional variance between lamina (~3-5mm). Pseudo-laminae of pyrite are common (2-6mm). Fractures with voided space are host to greenish dull yellow, euhedral, vitreous well cleaved crystals 1-3mm long, rich in Vanadium and Titanium. » ‹ @ 149.00 Galena bleb. The only one observed, it is hosted in a light grey silicified limestone that does not have any lead in it according to the NITON XRF machine › « 149.00- 150.40 Interval of poorly laminated to massive light grey limestone with <1% sub-rounded, elongate limestone clasts. » ‹ @ 150.20 A calcite vein occurs here with dark brown to grey brecciated pieces of crystal (~50/50 calcite to crystal). The crystals are distributed in a mosaic style that could be fit back together. Crystals are soft, fracture brittally, resinous lusture, opaque. Possibly siderite?› « 150.40- 151.80 Gradational transition from limestone at top of interval to calcareous mudstone at base. » ‹ @ 161.20 S0 defined by pyritic laminae. S0 tca 55° › ‹ @ 165.50 S0 defined by laminae. S0 tca 50° › ‹ @ 174.10 S0 defined by laminae. S0 tca 35° › ‹ @ 175.80 S0 defined by laminae S0 tca 40° › « 151.80- 177.60 The lower part of CCMS observed in this hole is pyritic (~1-2%) and has well defined laminae. Chert clasts do occur, they are minor in occurance however show up over ranges 30-50cm thick in a carbonaceous and calcareous mudstone that is otherwise indistinguishable from the other									



Hole Number:
XYC-236

Selwyn Chihong Mining Ltd.

#700-509 Richards Street

Vancouver, British Columbia

Canada, V6B 2Z6

Printed on: 2011/01/28

Diamond Drill Log

Comprehensive Report for Hole:

XYC-235

Hole No.: XYC-235	Depth: 168.50 m	Horizontal Length: 0.00 m	Project: 1710
Location Data:			
Property:	Selwyn Project	Claim Name:	X 13
Mining District:	Selwyn Basin	Grant Number:	Y 64538
Province/Territory:	Yukon		
UTM Co-Ordinates & Altitude of Drill Hole Collar:			
UTM Easting:	488698.37 m	True Azimuth:	213.0 °
UTM Northing:	6926265.46 m	Hole Angle:	-80.0 °
Elevation (m):	1574.11 m	NTS Name:	Placer Creek
		NTS Number:	105L06
Grid Co-Ordinates of Drill Hole Collar:			
Grid Easting (m):	0.00 m	Grid Name:	HP 06
Grid Northing (m):	0.00 m	Grid Type:	100m
Grid Azimuth:	273.0 °		
Dimond Drilling Contract:			
Drilled By:	CY-02	Date Drilling Start:	10/20/2010
		Date Finish:	10/25/2010
Diamond Drill Core:			
Logged By:	Kate Cameron / Graham	Date Logging Start:	11/06/2010
		Date Finish:	11/13/2010
Legend for Core Logging Codes: PAX			
Core Size:	NQ	Cemented:	Yes
Casing Depth:	9.00 m	Casing Pulled:	Yes
Water Depth:	0.00 m	Overburden Depth:	9.00 m
Level:	Section:	Drift:	

Selwyn Project

Diamond Drill Log

Survey Data for Hole

XYC-235

Hole Comments:

Wed, Oct 20 ---XYC-230 Shut down last night at 173m in CCMS since 158m. Will move to set up # 61 this morning

=====

Thu, Oct 21 --- Total depth 50m in USMS. 9m of casing, collared into USMS. They lost return last night at 45m, spent 4-5 hours conditioning hole, more hole conditioning may be required today before they can drill

=====

Fri, Oct 22 --- Total depth 83 in ACTM. USMS-ACTM contact 68.5m. Fault from 77m to 83m. No return on this hole, a tube was smashed into the bit last night, ruined core barrel and bit, rods had to be pulled. Generator failed last night, was dragged to camp this morning, can be replaced by generator in line for 3rd drill

=====

Sat, Oct 23 --- 16 bags of cement were put down the hole last night to try and fill all fractures; they are waiting another hour for it to set this morning and then will try drilling and hopefully get return. No core in past 24 hours.

=====

Sun, Oct 24 --- Put down 16 bags of cement as well as 16 buckets of Quickset, and let set for most of the day in an effort to plug fractures. When drilling commenced they only had approximately 6 feet of cement in the hole to drill through, indicating that the majority of cement was lost in fractures. Still no return, but drilling re-started last night and we are very hopeful that drilling will go well today. Currently at 92 meters, in a fault over the last meters with ~60% flt gg. From 86-88 meters we hit moderate to high grade ACTM. Will continue drilling.

=====

Mon, Oct 25 ---Shut down total depth 168.5m in CCMS when their bit went last night. ACTM from 68.5m to 141m. Moving to setup #35a at first light this morning.

<i>Depth</i>	<i>Dip</i>	<i>Azimuth</i>
0.00	-80.0	213.0
50.00	-80.0	211.8
101.00	-79.1	207.5
155.00	-79.1	208.6
167.00	-78.6	203.6

Selwyn Project Diamond Drill Log

Hole Number:
XYC-235

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%	
0.00	9.00	OVBR										
9.00	67.60	USMS	635901	64.50	66.00	1.50	0.07	0.67	1.00	20.00	0.10	
USMS – Upper Siliceous Mudstone Consists of interlaminated dark grey to black mudstone and light to medium grey chert. Regionally, a 1m thick graptolite zone occurs 15m below the top of the upper unit, this is usable as a horizon. The USMS is divided into 3 units. The Lower Unit contains abundant limestone concretions and Galena and sphalerite micro-concretions occur locally near the base of this unit. « gra , lm chrt -20.00% », « cg xtl sph crns ca 5.00-20.00cm », « bed chrt 10.00-15.00% » « 17.30- 21.10 With 40cm whole core in the middle. Flt »« Flt gg 25%»« Flt bx 25%»« Brco 25%» ◁ @ 26.10 S0 in planar parallel chert banding set. S0 tca 40° ▷ ◁ @ 50.00 S0 in light grey planar parallel chert banding set. S0 tca 45° ▷ « 55.40- 60.60 Flt »« Flt gg 5%»« Flt bx 45%»« Brco 30%»			635902	66.00	67.60	1.60	0.01	0.43	1.00	20.00	0.02	
67.60	148.00	ACTM	635903	67.60	68.00	0.40	0.04	0.32	3.00	5.00	0.13	
ACTM – Active Member The ACTM consists of a repetitive, possibly rhythmic, sequence of intercalated carbonaceous mudstone, cherty mudstone, chert and limestone and locally contains economically significant Zn and Pb sulphides (see bold marked facies), mainly in its sections with well developed lamination. Because of its heterogeneity, the member is distinctive and easily identified. ===== The ACTM has 8 different facies: ===== - GREY CHERT FACIES: Consists of laminated medium light grey to medium dark grey chert. Mineralization: 95-99% quartz and up to 5% secondary calcite.			635904	68.00	68.60	0.60	0.15	0.07	1.00	5.00	2.14	
			635905	68.60	69.20	0.60	1.60	3.78	3.00	190.00	0.42	
			635906	69.20	69.80	0.60	3.69	8.49	3.00	270.00	0.43	
			635907	69.80	71.10	1.30	2.03	8.14	3.00	260.00	0.25	
			635908	71.10	71.40	0.30	0.18	1.03	1.00	10.00	0.17	
			635909	71.40	71.90	0.50	3.02	8.74	3.00	210.00	0.35	
			635910	71.90	73.00	1.10	2.24	6.47	3.00	170.00	0.35	
			635911	71.90	73.00	1.10	1.31	5.05	1.00	130.00	0.26	
			635912	73.00	74.00	1.00	1.02	1.54	1.00	30.00	0.66	
			635913	74.00	74.30	0.30	0.06	0.05	1.00	5.00	1.20	
			635914	74.30	75.90	1.60	0.46	1.88	1.00	50.00	0.24	
			635915	75.90	76.90	1.00	0.19	1.61	1.00	30.00	0.12	
			635916	76.90	77.80	0.90	0.36	0.65	1.00	10.00	0.55	
			635917	77.80	78.30	0.50	0.45	2.07	1.00	60.00	0.22	
			635918	78.30	78.60	0.30	6.46	13.10	4.00	380.00	0.49	

Selwyn Project Diamond Drill Log

Hole Number:
XYC-235

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
- WHITISH GREY ZN-PB MUDSTONE FACIES: Is a laminated cherty rock containing up to 70% sulphides. Mineralization: quartz, sphalerite and galena are the major minerals with only minor amounts of pyrite and locally calcite. Sedimentary diagenetic structures are common and well displayed in the facies, such as: lamination, pseudo-beds, calcite nodules & limestone nodules and abundant water escape structures. Most obvious structure in facies is cross-cutting veins containing massive sphalerite and galena with minor pyrite. They range in width from 0.5 to 10mm. - THIN BEDDED CHERTY MUDSTONE FACIES: Consists of rhythmic intercalated laminae of chert, carbonaceous mudstone and minor micrite. This facies contains significant amounts of Zn and Pb sulphides. - CHERTY MUDSTONE FACIES: Consists of a greyish black monotonous siliceous, carbonaceous mudstone. It is most typically found overlying the thin bedded calcareous mudstone facies. - THIN BEDDED CALCAREOUS MUDSTONE FACIES: Consists of laminated carbonaceous mudstone containing 20-40% calcite, 40-55% quartz and 10-20% muscovite. Sulphides occur in laminae. In the XY area it is usually the lowest facies in the section to contain laminated sulphides. - CALCAREOUS MUDSTONE FACIES: Consists of grey to greyish black monotonous, calcareous siliceous carbonaceous mudstone. There are no feathery calcite beds or pyrite-calcite blebs in the facies, making it easily distinguishable from the CCMS. - GRADED LIMESTONE FACIES: Is a laminated argillaceous limestone with intercalated carbonaceous limestone laminae. The main rock type in the facies is laminated limestone with laminae up to 0.1-7mm thick. - LIGHT GREY BASAL LIMESTONE FACIES - LGLS: Consists of laminated			635919	78.60	80.20	1.60	0.19	0.78	1.00	30.00	0.24
			635920	80.20	80.20	0.00	0.01	0.01	1.00	5.00	2.00
			635921	80.20	81.80	1.60	0.99	4.24	1.00	90.00	0.23
			635922	81.80	82.80	1.00	1.02	8.05	2.00	190.00	0.13
			635923	82.80	84.70	1.90	2.23	7.19	4.00	210.00	0.31
			635924	84.70	86.00	1.30	1.43	3.29	1.00	90.00	0.43
			635925	86.00	87.20	1.20	6.91	21.48	5.00	710.00	0.32
			635926	87.20	87.90	0.70	6.42	20.92	5.00	630.00	0.31
			635927	87.90	89.40	1.50	2.13	4.99	2.00	140.00	0.43
			635928	89.40	90.80	1.40	0.32	0.50	1.00	10.00	0.64
			635929	90.80	92.00	1.20	1.20	3.01	1.00	80.00	0.40
			635930	92.00	92.60	0.60	0.09	0.50	1.00	10.00	0.18
			635931	92.60	92.60	0.00	6.29	7.00	72.00	190.00	0.90
			635932	92.60	94.30	1.70	1.69	5.15	2.00	130.00	0.33
			635933	94.30	94.60	0.30	1.15	4.88	1.00	140.00	0.24
			635934	94.60	95.20	0.60	1.47	6.69	1.00	210.00	0.22
			635935	95.20	96.50	1.30	0.84	4.62	1.00	130.00	0.18
			635936	96.50	97.00	0.50	2.60	8.40	2.00	180.00	0.31
			635937	97.00	98.30	1.30	1.35	5.99	1.00	130.00	0.23
			635938	98.30	99.20	0.90	0.64	2.42	1.00	70.00	0.26
			635939	99.20	100.00	0.80	0.51	1.65	1.00	40.00	0.31
			635940	100.00	101.00	1.00	0.18	0.13	1.00	5.00	1.38
			635941	100.00	101.00	1.00	0.35	0.38	1.00	5.00	0.92
			635942	101.00	101.90	0.90	1.10	5.20	1.00	120.00	0.21
			635943	101.90	102.60	0.70	2.16	3.00	1.00	70.00	0.72
			635944	102.60	103.00	0.40	1.28	4.16	1.00	90.00	0.31
			635945	103.00	103.70	0.70	0.23	2.00	1.00	40.00	0.12
			635946	103.70	104.40	0.70	0.08	0.01	1.00	5.00	8.00
			635947	104.40	105.50	1.10	0.02	0.01	1.00	5.00	4.00
			635948	105.50	106.00	0.50	0.07	0.01	1.00	5.00	14.00
			635949	106.00	107.10	1.10	0.10	0.10	1.00	5.00	1.00
			635950	107.10	107.10	0.00	0.01	0.01	1.00	5.00	2.00
			635951	107.10	107.60	0.50	0.04	0.06	1.00	5.00	0.67

Selwyn Project Diamond Drill Log

Hole Number:
XYC-235

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		argillaceous limestone. In the Anniv area it marks the end of the ACTM. It's not always present in the stratigraphy.									
		- BASAL FACIES: This is a highly contorted and locally foliated carbonaceous mudstone. Unlike the other facies it is not repeated higher in the member. It appears locally to contain the slip zone of a major slump. The facies has only been observed in the YX area. It is 0.1-2m thick. The facies consists of massive carbonaceous siliceous mudstone with lenses and laminae of contorted, slightly carbonaceous chert.	635952	107.60	108.30	0.70	0.11	0.62	1.00	20.00	0.18
			635953	108.30	109.00	0.70	0.20	0.07	1.00	5.00	2.86
			635954	109.00	109.50	0.50	0.47	0.63	1.00	20.00	0.75
			635955	109.50	110.00	0.50	0.22	1.03	1.00	30.00	0.21
			635956	110.00	111.00	1.00	0.42	0.36	1.00	20.00	1.17
			635957	111.00	112.00	1.00	0.24	0.80	1.00	20.00	0.30
			635958	112.00	112.80	0.80	0.17	0.49	1.00	5.00	0.35
			635959	112.80	113.30	0.50	0.41	1.22	3.00	40.00	0.34
			635960	113.30	113.30	0.00	1.41	2.89	17.00	180.00	0.49
			635961	113.30	114.80	1.50	0.07	1.01	1.00	30.00	0.07
		« 67.60- 68.00 Silicious laminated mudstone with some sphalerite mineralization in laminae. Dark grey to black. »	635962	114.80	116.00	1.20	0.28	0.59	1.00	20.00	0.47
			635963	116.00	116.90	0.90	1.06	4.64	4.00	130.00	0.23
		« 68.00- 68.60 Monotonous silicious mudstone. No mineralization. »	635964	116.90	118.10	1.20	0.06	0.14	1.00	5.00	0.43
			635965	118.10	118.60	0.50	0.05	0.09	1.00	5.00	0.56
			635966	118.60	119.50	0.90	0.01	0.02	1.00	5.00	0.50
		« 68.60- 69.20 Silicious dark grey to black mudstone with abundant sphalerite laminae. Visual estimate: 5% Zn. Quite a lot of pyrite as well. »	635967	119.50	120.90	1.40	0.01	0.18	1.00	5.00	0.06
			635968	120.90	121.60	0.70	0.19	0.72	1.00	30.00	0.26
			635969	121.60	122.30	0.70	1.36	8.88	2.00	290.00	0.15
		« 69.20- 69.80 Light-to-medium grey mudstone with galena and abundant calcite stringers. Possibly some sphalerite in weak laminae. »	635970	122.30	122.80	0.50	1.20	6.16	1.00	210.00	0.19
			635971	122.30	122.80	0.50	1.32	5.73	2.00	200.00	0.23
			635972	122.80	123.10	0.30	5.02	12.59	3.00	530.00	0.40
		« 69.80- 71.10 Silicious laminated mudstone with some sphalerite mineralization in laminae. Dark grey to black. »	635973	123.10	124.10	1.00	1.18	7.12	2.00	190.00	0.17
			635974	124.10	124.40	0.30	1.35	11.17	3.00	260.00	0.12
			635975	124.40	124.90	0.50	0.67	1.99	1.00	70.00	0.34
		« 71.10- 71.40 Limestone. Light grey. Coarse, massive. No visible mineralization. »	635976	124.90	125.60	0.70	0.20	1.53	1.00	40.00	0.13
			635977	125.60	126.00	0.40	0.01	0.13	1.00	5.00	0.08
			635978	126.00	126.30	0.30	0.27	2.00	1.00	60.00	0.14
		« 71.40- 71.90 Silicious laminated mudstone with some sphalerite mineralization in laminae. Dark grey to black. »	635979	126.30	127.00	0.70	0.21	1.71	1.00	50.00	0.12
			635980	127.00	127.00	0.00	0.01	0.01	1.00	5.00	2.00
			635981	127.00	127.50	0.50	0.03	0.37	1.00	10.00	0.08
		« 71.90- 73.00 Black to dark grey mudstone with calcite veins and very low mineralization (aside from pyrite). Laminated. »	635982	127.50	128.30	0.80	0.06	0.93	1.00	30.00	0.06
			635983	128.30	129.00	0.70	0.04	0.97	1.00	30.00	0.04
			635984	129.00	129.50	0.50	2.06	9.79	2.00	260.00	0.21
		« 73.00- 74.00 Medium grey calcite mudstone with some limestone clasts.	635985	129.50	130.20	0.70	0.34	1.54	1.00	50.00	0.22

Selwyn Project Diamond Drill Log

Hole Number:
XYC-235

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
Low mineralization, weakly laminated. »			635986	130.20	131.00	0.80	0.59	1.97	1.00	60.00	0.30
« 74.00- 74.30 Limestone, light grey. Coarse, massive. No visible mineralization. »			635987	131.00	131.50	0.50	1.15	4.93	1.00	140.00	0.23
			635988	131.50	132.30	0.80	0.81	4.10	1.00	100.00	0.20
			635989	132.30	132.80	0.50	0.72	4.89	1.00	120.00	0.15
« 74.30- 75.90 Medium grey, weakly laminated mudstone. Variable weak calcareous sections. No visible mineralization. »			635990	132.80	132.80	0.00	6.10	7.04	70.00	190.00	0.87
			635991	132.80	133.60	0.80	0.06	0.77	1.00	20.00	0.08
			635992	133.60	134.00	0.40	3.02	13.62	3.00	330.00	0.22
« 75.90- 77.80 Dark grey to black mudstone with very weak laminae. No visible mineralization. »			635993	134.00	134.70	0.70	4.98	27.97	6.00	580.00	0.18
			635994	134.70	135.30	0.60	0.61	2.29	1.00	60.00	0.27
			635995	135.30	136.00	0.70	1.19	2.67	1.00	70.00	0.45
« 76.90- 77.80 Slick-n-slided surfaces present. Flt »« Flt gg 10%»« Flt bx 90%»			635996	136.00	136.60	0.60	2.55	14.26	2.00	330.00	0.18
			635997	136.60	137.00	0.40	3.09	27.56	6.00	560.00	0.11
			635998	137.00	137.70	0.70	0.85	3.00	1.00	70.00	0.28
« 77.80- 78.30 Weakly laminated, dark grey limestone. No visible mineralization. »			635999	137.70	138.00	0.30	1.26	3.46	1.00	90.00	0.36
			636000	138.00	138.60	0.60	0.42	1.90	1.00	50.00	0.22
			634151	138.00	138.60	0.60	1.80	2.55	2.00	60.00	0.71
« 78.30- 78.60 Dark grey mudstone with sphalerite laminae and clasts of limestone. »			634152	138.60	139.10	0.50	1.81	2.35	2.00	60.00	0.77
			634153	139.10	139.40	0.30	0.20	0.63	3.00	10.00	0.32
			634154	139.40	139.80	0.40	1.65	4.85	3.00	120.00	0.34
« 78.60- 80.20 Medium grey, coarse, massive limestone. No visible mineralization. »			634155	139.80	141.00	1.20	0.03	0.02	1.00	5.00	1.50
			634156	141.00	142.30	1.30	0.02	0.04	1.00	5.00	0.50
			634157	142.30	143.30	1.00	0.10	0.04	1.00	5.00	2.50
« 79.30- 84.60 Overlaps next sub-unit. Flt »« Flt gg 15%»« Flt bx 55%»« Brco 20%»			634158	143.30	143.70	0.40	0.11	0.13	1.00	5.00	0.85
			634159	143.70	144.40	0.70	0.24	0.76	1.00	20.00	0.32
			634160	144.40	144.40	0.00	0.01	0.01	1.00	5.00	2.00
« 80.20- 84.70 Weakly laminated limestone. Some sphalerite visible in laminae. »			634161	144.40	144.80	0.40	0.59	1.13	3.00	30.00	0.52
			634162	144.80	145.40	0.60	0.15	1.05	1.00	20.00	0.14
			634163	145.40	145.70	0.30	0.30	0.51	1.00	20.00	0.59
« 81.00- 83.10 Fracture infill contains well-formed euhedral crystals that look somewhat like calcite. However, they are tinted yellowish, do not effervesce strongly and test high for V and T, with the Niton. [Could be Fluorite]»			634164	145.70	146.10	0.40	0.21	0.62	3.00	20.00	0.34
			634165	146.10	147.00	0.90	0.14	1.01	3.00	30.00	0.14
			634166	147.00	148.00	1.00	0.01	0.01	1.00	5.00	2.00
« 84.70- 86.00 Weakly laminated mid of light grey and dark grey											

Selwyn Project Diamond Drill Log

Hole Number:
XYC-235

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		mudstone with calcite veins. » « 86.00- 87.90 Medium grey, laminated, micro-fractured mudstone. Galena visible in veins along micro-fractures. » « 87.90- 89.40 Weakly laminated, medium to dark grey mudstone. No visible mineralization. Carbonaceous. » « 89.40- 90.80 Limestone with lots of calcite veins and stringers. Broken » « 90.80- 92.00 Carbonaceous black mudstone. No visible mineralization. All gouge. » « 92.00- 92.60 Very light grey limestone with abundant calcite stringers. » « 92.60- 94.30 Mix of black carbonaceous mudstone and limestone. No visible mineralization. Broken up. » « 94.30- 101.00 Blocky ground throughout interval of light grey limestone with abundant calcite and quartz veins. Intervalated with minor calcareous mudstone. No visible mineralization. Flt »« Flt gg 7%»« Flt bx 53%»« Brco 40%» « 101.00- 106.00 Still in blocky ground. Intercalated limestone as described with contorted laminated slightly metalliferous mudstone. Calcite-quartz veining is pervasive through both major lithologies. » « 103.80- 104.00 Flt »« Flt gg 50%»« Flt bx 50%» « 106.00- 106.60 Flt »« Flt gg 30%»« Flt bx 70%» « 107.10- 109.50 Medium grey finely cross-laminated mudstone. Minor rounded limestone concretions. Pervasive calcite-quartz veining. Highly									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-235

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		fractured with a weakly developed cleavage. Deformation of laminae around limestone inclusions. » « 109.50- 112.80 Laminated, graded, variable muddy limestone. Calcic laminae, pyritic laminae, fairly planar fabric. » « 113.30- 119.50 Broken, brecciated, reconstituted in many cases, limestone and mudstone. Flt »« Flt gg 45%»« Flt bx 30%»« Brco 25%» « 119.50- 121.60 Carbonaceous, slightly silicious, dark grey, weakly laminated mudstone, very low grade, no visible mineralization. » « 121.60- 125.30 Laminated light grey, brownish, yellowish sphalerite and galena enriched laminae. Some sections ~5-10cm of light grey-yellowish laminae with discordant galena and mud veinlets. Abundant pyritic laminae. Limestone clasts deform surrounding laminae. » « 124.90- 127.50 Medium grey laminated low grade silicious mudstone. Graded in a normal fashion. Abundant irregular and cusped orthogonal to S0 stylolites. » « 127.50- 129.00 Dark grey carbonaceous pyritic mudstone, laminated. » « 129.00- 133.60 Intercalated laminated light grey limestone and calcareous mudstone, with one section in the upper interval of base metal enriched laminae and limestone clasts. » « 133.60- 134.00 Laminated metalliferous mud-laminae interlaminated with bluish light grey limestone. The interval is mostly limestone. Discordant dissolution seams are enriched with fine grained galena and sphalerite. » « 134.00- 134.70 Semi-massive to massive sulphite breccia. Angular clasts of mudstone limestone and sphalerite/pyrite massive sulphides. » « 134.70- 136.00 Laminated, weakly calcareous dark grey mudstone, with									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-235

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		some sphalerite and pyrite enriched laminae. Rounded clasts of fine grained laminated limestone. »									
		« 136.00- 137.00 Laminated brown, and variably light grey metalliferous mudstone with discordant dissolution seams remobilizing galena and coarse sphalerite with mud (1-2mm thick). Laminae are variably enriched with fine grained sphalerite and interstitial galena. »									
		« 137.00- 139.80 Laminated calcareous mudstone interbedded with sections of low-grade limestone clastic carbonaceous mudstone. Discordant veins enriched with galena (<1%). Sulphide enriched laminae as described. Abundant quartz-calcite veining at contacts between contorted depositional layers. »									
		« 139.80- 148.00 Interval of laminated, crossbedded limestone of fairly low grade, intercalated with minor pyritic and carbonaceous mudstone. Many limestone clasts throughout. Broken up pseudo-beds of massive pyrite. Quartz and calcite veins ~1cm thick continue to mark major depositional contacts. Laminations are highly deformed. »									
148.00	168.50	CCMS	634167	148.00	148.70	0.70	0.04	0.02	7.00	5.00	2.00
		CCMS – Calcareous Mudstone	634168	148.70	149.20	0.50	0.09	0.81	5.00	50.00	0.11
			634169	149.20	150.00	0.80	0.04	0.57	6.00	40.00	0.07
			634170	150.00	150.00	0.00	1.45	2.95	20.00	180.00	0.49
		Massive, calcareous, carbonaceous, dark grey mudstone. Most of the member is massive, but rare poorly defined bedding and pyrite-calcite micro-concretions are present. Most diagnostic structures are feathery calcite beds (=thin calcite-cemented concretions, many of them contain pyrite cores) and calcite pseudo-beds (= fibrous calcite vein parallel to bedding).									
		« lm ca 5.00-10.00mm », « nodules py -3.00% 2.00-20.00mm »									
		« 148.00- 168.50 Fairly competent carbonaceous mudstone, pyritic blebs and laminae. Fractures often infilled with calcite may brecciate rock a bit. »									
		< @ 158.40 S0 defined by wispy conformable calcite, planar. This is typical of entire interval with exception of a few 20-40cm sections with wavy graded									



Hole Number:
XYC-235

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

[illegible]

Diamond Drill Log

Comprehensive Report for Hole:

XYC-234

Hole No.: XYC-234	Depth: 188.00 m	Horizontal Length: 0.00 m	Project: 1710
Location Data:			
Property:	Selwyn Project	Claim Name:	X 16
Mining District:	Selwyn Basin	Grant Number:	Y 64541
Province/Territory:	Yukon		
UTM Co-Ordinates & Altitude of Drill Hole Collar:			
UTM Easting:	489099.95 m	True Azimuth:	187.0 °
UTM Northing:	6926148.54 m	Hole Angle:	-66.0 °
Elevation (m):	1608.29 m	NTS Name:	Placer Creek
		UTM Datum:	NAD 83
		UTM Grid Zone:	9
		NTS Number:	105I06
Grid Co-Ordinates of Drill Hole Collar:			
Grid Easting (m):	0.00 m	Grid Name:	HP 06
Grid Northing (m):	0.00 m	Grid Type:	100m
Grid Azimuth:	243.0 °		
Dimond Drilling Contract:			
Drilled By:	CY-01	Date Drilling Start:	10/19/2010
		Date Finish:	10/22/2010
Diamond Drill Core:			
Logged By:	Kate Cameron / Jelle De	Date Logging Start:	11/01/2010
		Date Finish:	11/16/2010
Legend for Core Logging Codes: PAX			
Core Size:	NQ	Cemented:	Yes
Casing Depth:	6.70 m	Casing Pulled:	Yes
Water Depth:	0.00 m	Overburden Depth:	6.70 m
Level:	Section:	Drift:	

Selwyn Project

Diamond Drill Log

Survey Data for Hole

XYC-234

Hole Comments:

Wed, Oct 20 ---XYC-232 was shut down yesterday at 179m in CCMS. Moved to setup # 54. XYC-234 total depth 23m. Only up to 20m was emptied into the box this morning, that was 15cm of black broken core, not identifiable. No day shift driller this morning due to shift change

=====

Thu, Oct 21 --- Total depth 71m in USMS. Drilling is going well

=====

Fri, Oct 22 --- In ACTM at 149 meters. ACTM-USMS contact at approximately 127 meters. Mineralization is generally moderate to strong throughout the intersection so far. No problems.

<i>Depth</i>	<i>Dip</i>	<i>Azimuth</i>
0.00	-66.0	187.0
14.00	-65.5	187.0
50.00	-64.1	187.5
100.00	-62.2	188.9
151.00	-60.9	191.4
187.40	-61.1	193.1

Selwyn Project Diamond Drill Log

Hole Number:
XYC-234

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
0.00	6.70	OVBR									
6.70	126.60	USMS	635401	125.00	125.90	0.90	0.01	0.47	1.00	20.00	0.02
USMS – Upper Siliceous Mudstone			635402	125.90	126.60	0.70	0.12	0.37	1.00	20.00	0.32
Consists of interlaminated dark grey to black mudstone and light to medium grey chert. Regionally, a 1m thick graptolite zone occurs 15m below the top of the upper unit, this is usable as a horizon. The USMS is divided into 3 units. The Lower Unit contains abundant limestone concretions and Galena and sphalerite micro-concretions occur locally near the base of this unit. « gra , lm chrt -20.00% », « cg xtl sph crns ca 5.00-20.00cm », « bed chrt 10.00-15.00% », Typical USMS, frequent pyrite blebs, bedding is variable. « 6.70- 23.50 Brk zone, near surface. Mostly whole core, but broken frequently. »« brk pc 15%»« bx 5%»« flt gg 5%» « 38.50- 38.80 Low mineralized zone. Sph laminae are weak but visible. Niton Pb 0.33%, Zn 2.3% » « 41.30- 41.80 Highly mnx section. Lt grey and lt brown. Fine laminae, densely packed. Mainly sph. Ga only visible by its effect on colour (grey). »« Niton Pb 6.36% Zn 11.92% » < @ 44.80 Parallel chert banding S0 tca 70° > « 42.10- 43.10 Brk « whole 50%»« brk 20%»« bx 30%»« gg » « 49.90- 52.50 Brk »« whole 40%»« brk 20%»« bx 30%»« gg 10%» < @ 68.30 Parallel planar disseminated ca/py laminae/bands S0 tca 80° > < @ 101.70 Planar parallel chert bands S0 tca 70° > < @ 111.20 Defined by parallel chert bands S0 tca 74° > « 117.80- 123.60 FLT »« flt gg 15%»« bx 25%»« brkn 50%»											

Selwyn Project Diamond Drill Log

Hole Number:
XYC-234

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
126.60	153.30	ACTM									
<i>ACTM – Active Member</i>			635403	126.60	127.40	0.80	1.98	4.89	3.00	240.00	0.40
<i>The ACTM consists of a repetitive, possibly rhythmic, sequence of intercalated carbonaceous mudstone, cherty mudstone, chert and limestone and locally contains economically significant Zn and Pb sulphides (see bold marked facies), mainly in its sections with well developed lamination. Because of its heterogeneity, the member is distinctive and easily identified.</i> ===== <i>The ACTM has 8 different facies:</i> ===== - GREY CHERT FACIES: Consists of laminated medium light grey to medium dark grey chert. Mineralization: 95-99% quartz and up to 5% secondary calcite. - WHITISH GREY ZN-PB MUDSTONE FACIES: Is a laminated cherty rock containing up to 70% sulphides. Mineralization: quartz, sphalerite and galena are the major minerals with only minor amounts of pyrite and locally calcite. Sedimentary diagenetic structures are common and well displayed in the facies, such as: lamination, pseudo-beds, calcite nodules & limestone nodules and abundant water escape structures. Most obvious structure in facies is cross-cutting veins containing massive sphalerite and galena with minor pyrite. They range in width from 0.5 to 10mm. - THIN BEDDED CHERTY MUDSTONE FACIES: Consists of rhythmic intercalated laminae of chert, carbonaceous mudstone and minor micrite. This facies contains significant amounts of Zn and Pb sulphides. - CHERTY MUDSTONE FACIES: Consists of a greyish black monotonous siliceous, carbonaceous mudstone. It is most typically found overlying the thin bedded calcareous mudstone facies.			635404	127.40	128.00	0.60	1.82	12.71	1.00	590.00	0.14
			635405	128.00	128.30	0.30	6.83	14.29	1.00	720.00	0.48
			635406	128.30	129.10	0.80	2.11	9.65	2.00	270.00	0.22
			635407	129.10	129.70	0.60	2.87	10.59	1.00	290.00	0.27
			635408	129.70	130.10	0.40	0.21	1.21	1.00	30.00	0.17
			635409	130.10	130.80	0.70	0.11	0.49	1.00	10.00	0.22
			635410	130.80	131.60	0.80	0.02	0.32	1.00	5.00	0.06
			635411	130.80	131.60	0.80	0.02	0.21	1.00	5.00	0.10
			635412	131.60	133.00	1.40	1.10	0.92	1.00	30.00	1.20
			635413	133.00	134.30	1.30	2.68	2.27	1.00	60.00	1.18
			635414	134.30	134.60	0.30	4.70	17.27	4.00	600.00	0.27
			635415	134.60	134.80	0.20	1.88	29.85	1.00	780.00	0.06
			635416	134.80	135.60	0.80	0.57	0.74	1.00	20.00	0.77
			635417	135.60	136.60	1.00	0.14	0.29	1.00	5.00	0.48
			635418	136.60	137.30	0.70	1.76	4.80	1.00	130.00	0.37
			635419	137.30	138.30	1.00	0.94	3.47	1.00	100.00	0.27
			635420	138.30	138.30	0.00	0.01	0.02	1.00	5.00	0.50
			635421	138.30	138.80	0.50	4.62	17.39	3.00	430.00	0.27
			635422	138.80	140.00	1.20	0.75	3.61	1.00	80.00	0.21
			635423	140.00	140.60	0.60	2.22	2.38	1.00	60.00	0.93
			635424	140.60	141.60	1.00	2.71	8.76	3.00	250.00	0.31
			635425	141.60	143.00	1.40	1.10	5.26	1.00	150.00	0.21
			635426	143.00	144.60	1.60	0.73	4.47	1.00	130.00	0.16
			635427	144.60	144.80	0.20	6.97	10.86	1.00	500.00	0.64
			635428	144.80	145.80	1.00	0.20	0.13	1.00	5.00	1.54
			635429	145.80	146.70	0.90	0.16	0.85	1.00	20.00	0.19
			635430	146.70	146.70	0.00	5.98	7.03	71.00	190.00	0.85
			635431	146.70	147.50	0.80	0.38	1.18	1.00	30.00	0.32
			635432	147.50	149.00	1.50	0.28	1.19	1.00	30.00	0.24
			635433	149.00	150.20	1.20	0.16	0.44	1.00	10.00	0.36
			635434	150.20	151.30	1.10	0.15	1.23	1.00	40.00	0.12
			635435	151.30	152.40	1.10	2.64	1.73	5.00	40.00	1.53

Selwyn Project Diamond Drill Log

Hole Number:
XYC-234

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		- THIN BEDDED CALCAREOUS MUDSTONE FACIES: Consists of laminated carbonaceous mudstone containing 20-40% calcite, 40-55% quartz and 10-20% muscovite. Sulphides occur in laminae. In the XY area it is usually the lowest facies in the section to contain laminated sulphides. - CALCAREOUS MUDSTONE FACIES: Consists of grey to greyish black monotonous, calcareous siliceous carbonaceous mudstone. There are no feathery calcite beds or pyrite-calcite blebs in the facies, making it easily distinguishable from the CCMS. - GRADED LIMESTONE FACIES: Is a laminated argillaceous limestone with intercalated carbonaceous limestone laminae. The main rock type in the facies is laminated limestone with laminae up to 0.1-7mm thick. - LIGHT GREY BASAL LIMESTONE FACIES - LGLS: Consists of laminated argillaceous limestone. In the Anniv area it marks the end of the ACTM. It's not always present in the stratigraphy. - BASAL FACIES: This is a highly contorted and locally foliated carbonaceous mudstone. Unlike the other facies it is not repeated higher in the member. It appears locally to contain the slip zone of a major slump. The facies has only been observed in the YX area. It is 0.1-2m thick. The facies consists of massive carbonaceous siliceous mudstone with lenses and laminae of contorted, slightly carbonaceous chert. « 126.60- 129.70 Siliceous mdst with well developed lamination. Locally thick bands of high grade mineralization. 8% Zn, 3% Pb » « 129.70- 130.10 Limestone (0.5% Zn) » « 130.10- 131.60 Siliceous to faintly calcareous mdst, locally thin beds. Barren »	635436	152.40	153.30	0.90	6.22	0.69	14.00	20.00	9.01

Selwyn Project Diamond Drill Log

Hole Number:
XYC-234

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
« 131.60- 134.30 Siliceous, carbonaceous mdst. No lamination or bedding. (2% Zn) »											
« 134.30- 134.60 Siliceous mdst with half of the section showing well developed lamination. (>20% Zn + Pb). High grade mineralization. »											
« 134.60- 134.80 Calcareous mdst rich in sph. (>20% Zn, 4% Pb) »											
« 134.80- 136.60 Dominantly limestone. <1% Zn + Pb »											
« 136.60- 137.30 Mainly slightly calcareous mdst with poorly to moderately developed lamination. (3% Zn, 1% Pb) »											
« 137.30- 145.80 Section of alternating lmst (some of which is mineralized) and calcareous mineralized mdst with moderately to well developed lams. (4% Zn, 1.5% Pb) »											
« 145.80- 147.50 Siliceous carbonaceous mdst. Minor lmst. Poorly mineralized. Rare visible galena vein. (<1% Zn + Pb) »											
« 147.50- 150.20 Dominantly Limestone (~1% Zn + Pb) »											
« 150.20- 153.30 Calcareous mdst and lmst. More carbonaceous and richer in calcite veins than previous range feature. Minor visible ga veins. (1% Zn, 2.5% Pb) »											
« 153.30- 160.00 No basal lt grey lmst at the end of ACTM. This fault likely shortened the ACTM intersection FLT »« flt gg 20%»« flt bx 30%»« brkn 35%»											
153.30	188.00	CCMS	635437	153.30	154.00	0.70	0.04	0.24	1.00	5.00	0.17
CCMS – Calcareous Mudstone			635438	154.00	154.50	0.50	0.01	0.03	1.00	5.00	0.33
Massive, calcareous, carbonaceous, dark grey mudstone. Most of the member is massive, but rare poorly defined bedding and pyrite-calcite micro-concretions are present. Most diagnostic structures are feathery calcite beds (=thin											

Selwyn Project Diamond Drill Log

Hole Number:
XYC-234

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		calcite-cemented concretions, many of them contain pyrite cores) and calcite pseudo-beds (= fibrous calcite vein parallel to bedding). « lm ca 5.00-10.00mm », « nodules py -3.00% 2.00-20.00mm », Not typical CCMS. Not as carbonaceous. More than usual limestone concretions. Faintly calcareous mudstone. < @ 164.50 Defined by pyrite band S0 tca 63° > < @ 170.20 Defined by pyrite band S0 tca 75° > < @ 180.00 Defined by changing amounts of argillaceous material S0 tca 62° >									
188.00	188.00	EOH									

Diamond Drill Log

Comprehensive Report for Hole:

XYC-233

Hole No.: XYC-233	Depth: 719.10 m	Horizontal Length: 0.00 m	Project: 1710
Location Data:			
Property:	Selwyn Project	Claim Name:	X46
Mining District:	Selwyn Basin	Grant Number:	Y 64679
Province/Territory:	Yukon		
UTM Co-Ordinates & Altitude of Drill Hole Collar:			
UTM Easting:	487349.32 m	True Azimuth:	23.0 °
UTM Northing:	6927161.56 m	Hole Angle:	-63.0 °
Elevation (m):	1420.90 m	NTS Name:	Placer Creek
		NTS Number:	105L06
Grid Co-Ordinates of Drill Hole Collar:			
Grid Easting (m):	0.00 m	Grid Name:	HP 06
Grid Northing (m):	0.00 m	Grid Type:	100m
Grid Azimuth:	83.0 °		
Dimond Drilling Contract:			
Drilled By:	NL-03	Date Drilling Start:	10/18/2010
		Date Finish:	11/2/2010
Diamond Drill Core:			
Logged By:	Helena Kuikka/Gabe Xue	Date Logging Start:	01/19/2011
		Date Finish:	04/18/2011
Legend for Core Logging Codes: PAX			
Core Size:	NQ/BQ	Cemented:	Yes
Casing Depth:	9.10 m	Casing Pulled:	
Water Depth:	0.00 m	Overburden Depth:	9.10 m
Level:	Section:	Drift:	

Selwyn Project

Diamond Drill Log

Survey Data for Hole

XYC-233

Hole Comments:

Tue, Oct 19 --- Completed XYC-223 yesterday and moved to setup #49 on the same pad. The azimuth was changed from 20 degrees to 15 degrees for two reasons: First, at the time of completion of XYC-223 the drill was measured at an orientation of 23 degrees, so going to 20 degrees would have only meant a shift of 3 degrees. Secondly, XYC-223 deviated to the east by at least 13 degrees over the course of drilling, so it is anticipated that XYC-233, drilling at a similar orientation, on essentially the same spot, with the same drill, will also deviate to the east. By starting at 15 degrees as opposed to 20 degrees on XYC-233, we should come closer to hitting the intended target, while avoiding redundancy with the last hole. Night shift put down 30 feet of casing and drilled to 16 meters through broken, faulted rock. The minimal core observed is dark grey mudstone; difficult to determine the unit with any certainty at this time.

=====

Wed, Oct 20 --- Collared into and still drilling through Active Member, primarily low to medium grade at first inspection. Core to bedding angle is very low, generally between 0 and 30 degrees. Drilling is going too well.

=====

Thu, Oct 21 --- Still in Active member at 262 meters, drilling still going fast. Mostly low-medium grade, but we have definitely seen some short ranges that are higher in grade. Core-bedding angle has steepened up to 20-40 degrees over the last 100-150 meters, suggesting true thickness may be excellent, though bedding is of course unreliable in ACTM.

=====

Fri, Oct 22 --- Mineralization ends at approximately 260 meters; now at 332 meters in what is either barren ACTM or USMS just above ACTM. Bedding-core angle continues to be very low. Fault zone from 301 meters to current depth.

=====

Sat, Oct 23 --- Drilling through largely barren rock at 380 meters, although mineralization was observed sporadically over the past 50 meters. Rock continues to primarily resemble USMS right above the USMS-ACTM contact, or barren ACTM. Due to the presence of sporadic mineralization will tentatively call it all ACTM, will revise upon detailed logging. Drilling going well.

=====

Sun, Oct 24 --- Consistently good drilling from this rig through broken rock at 250 meters. The core is almost certainly CCMS; all traces of ACTM gone now. Anticipating the fault that XYC-223 hit.

=====

Mon, Oct 25 --- Drilling through extremely broken-up CCMS (probably) at 499 meters. In a large fault now from 481 meters to current depth. No mechanical problems to report.

=====

Tue, Oct 26 --- Still drilling through broken-up, dark grey mudstone at 550.40 meters. The core is most likely CCMS, though not quite typical. We are still drilling at an acute angle to bedding. No sign yet of the fault that took us back to FLMD in XYC-223, and we are considerably deeper than we were in XYC-223 when we hit that fault. Continuing drilling. This rig continues to perform very well, even at depth, with Mark and Josh drilling.

=====

Wed, Oct 27 --- Finally hit the fault at 583.3-585.8 meters. Now in FLMD, as hoped for, at 608 meters. The hole

Selwyn Project

Diamond Drill Log

Survey Data for Hole

XYC-233

is getting quite tight, according to the drillers, and they are unsure about how much deeper the hole can go. I told them to do their best to prepare to go considerably deeper.

=====

Thu, Oct 28 --- In FLMD at 631.6 meters. Yesterday DS could not get to bottom; NS got to bottom and drilled 24 meters. The hole is very tight and they did not feel that they could continue much further with NQ. Therefore we reduced to BQ this morning, will drill through core barrel and continue (to save several hours labour), hopefully all the way to next ACTM intersection.

=====

Fri, Oct 29 --- Reduced to BQ yesterday but DS used too much bentonite and had a very difficult time going down with the BQ rods. Last night NS got the BQ rods almost to the bit, so coring should re-start today. So it goes.

=====

Sat, Oct 30 --- The transmission shifter broke last night, and NS had to take one from NL-02, which had no night shift. Drilled 9.1m to 640 total depth. In definite USMS. FLMD-USMS contact at 629.4 meters.

=====

Sun, Oct 31 --- Dayshift drilled 13 meters yesterday to 654 meters in competent USMS. I was informed late last night, long after NL-02 setup back on XYC-220, that No Limit only has one set of BQ jaws for the CS-1000 drills (NL-02 and NL-03). I do not believe anyone on site from No Limit knew this until they went looking for the second set. I therefore had to decide last night to put either NL-02 or NL-03 on standby, and chose NL-03 because we had already spent so much time and effort getting NL-02 back onto XYC-220. The nightshift driller for NL-03 quit when Keith told him this, but he may be convinced to stay. There seems to be no limit to the problems lately...

=====

Mon, Nov 01 --- Hit ACTM at approximately 663 meters, drilling now in ACTM, possibly basal limestone, at 689 meters. We will likely drill through the day, possibly shutting down tonight given lithology.

=====

Tue, Nov 02 --- In CCMS at 711.7 meters; contact at 689 meters. The shutdown will take a shift and a half, so we will almost certainly get them shutting down mid-day today, after another check of the core. This way they can be ready to move in the morning.

=====

Wed, Nov 03 --- Shut down yesterday afternoon in CCMS at 719.1 meters. Pulled the all of the BQ rods out yesterday but could not free the NQ rods, however, even after the most experienced driller working on it all night. The No Limit cutter is still not working, and No Limit is currently looking to borrow a cutter from Cyr, but they can't find their cutter either, at least for now. We won't be able to do much here until we somehow regain the ability to cut rods.

=====

Thu, Nov 04 --- The NQ rod cutter was fixed yesterday afternoon, and the rods were successfully cut above the point at which they were stuck. The rods were cut at approximately 517 meters, which resulted in approximately 114 meters of rods left in the hole, including the core barrel. I would call it an incomplete victory. This morning they will cement the bottom 80 meters, put a Van Ruth plug in at approximately 300 meters, and cement to the top of the hole. Hopefully they are ready to begin the long move to the Don Zone this afternoon. They will go to setup # d2/d3, and commence DON-151.

Selwyn Project

Diamond Drill Log

Survey Data for Hole

XYC-233

=====

Fri, Nov 05 --- Packed up and ready to move. Will move to Don Zone setup d2/d3 today for DON-151.

<i>Depth</i>	<i>Dip</i>	<i>Azimuth</i>
0.00	-63.0	23.0
48.20	-62.0	23.5
93.90	-59.9	23.6
139.60	-58.7	23.3
185.30	-58.0	24.4
230.10	-57.8	27.3
276.80	-56.6	28.7
321.60	-55.1	27.4
368.20	-53.6	28.5
413.90	-53.0	28.9
459.60	-52.8	31.1
505.40	-52.6	31.7
550.60	-51.2	34.4
601.60	-50.1	34.1
666.00	-46.9	34.3
700.10	-43.4	34.5

Selwyn Project Diamond Drill Log

Hole Number:
XYC-233

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
0.00	9.10	OVBR									
9.10	254.10	ACTM	630101	9.10	11.00	1.90					
<i>ACTM – Active Member</i> <i>The ACTM consists of a repetitive, possibly rhythmic, sequence of intercalated carbonaceous mudstone, cherty mudstone, chert and limestone and locally contains economically significant Zn and Pb sulphides (see bold marked facies), mainly in its sections with well developed lamination. Because of its heterogeneity, the member is distinctive and easily identified.</i> ===== <i>The ACTM has 8 different facies:</i> ===== - GREY CHERT FACIES: <i>Consists of laminated medium light grey to medium dark grey chert. Mineralization: 95-99% quartz and up to 5% secondary calcite.</i> - WHITISH GREY ZN-PB MUDSTONE FACIES: <i>Is a laminated cherty rock containing up to 70% sulphides. Mineralization: quartz, sphalerite and galena are the major minerals with only minor amounts of pyrite and locally calcite. Sedimentary diagenetic structures are common and well displayed in the facies, such as: lamination, pseudo-beds, calcite nodules & limestone nodules and abundant water escape structures. Most obvious structure in facies is cross-cutting veins containing massive sphalerite and galena with minor pyrite. They range in width from 0.5 to 10mm.</i> - THIN BEDDED CHERTY MUDSTONE FACIES: <i>Consists of rhythmic intercalated laminae of chert, carbonaceous mudstone and minor micrite. This facies contains significant amounts of Zn and Pb sulphides.</i> - CHERTY MUDSTONE FACIES: <i>Consists of a greyish black monotonous siliceous, carbonaceous mudstone. It is most typically found overlying the thin bedded calcareous mudstone facies.</i>			630102	11.00	13.00	2.00					
			630103	13.00	14.90	1.90					
			630104	14.90	16.10	1.20					
			630105	16.10	17.30	1.20					
			630106	17.30	18.80	1.50					
			630107	18.80	20.00	1.20					
			630108	20.00	21.60	1.60					
			630109	21.60	22.80	1.20					
			630110	22.80	24.80	2.00					
			630111	22.80	24.80	2.00					
			630112	24.80	26.70	1.90					
			630113	26.70	26.70	0.00					
			630114	26.70	27.90	1.20					
			630115	27.90	29.60	1.70					
			630116	29.60	33.00	3.40					
			630117	33.00	34.70	1.70					
			630118	34.70	36.00	1.30					
			630119	36.00	36.50	0.50					
			630120	36.50	36.50	0.00					
			630121	36.50	36.90	0.40					
			630122	36.90	38.10	1.20					
			630123	38.10	38.60	0.50					
			630124	38.60	39.40	0.80					
			630125	39.40	40.40	1.00					
			630126	40.40	41.10	0.70					
			630127	41.10	41.70	0.60					
			630128	41.70	42.80	1.10					
			630129	42.80	43.60	0.80					
			630130	43.60	43.60	0.00					
			630131	43.60	44.30	0.70					
			630132	44.30	45.10	0.80					

Selwyn Project Diamond Drill Log

Hole Number:
XYC-233

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
- <i>THIN BEDDED CALCAREOUS MUDSTONE FACIES: Consists of laminated carbonaceous mudstone containing 20-40% calcite, 40-55% quartz and 10-20% muscovite. Sulphides occur in laminae. In the XY area it is usually the lowest facies in the section to contain laminated sulphides.</i> - <i>CALCAREOUS MUDSTONE FACIES: Consists of grey to greyish black monotonous, calcareous siliceous carbonaceous mudstone. There are no feathery calcite beds or pyrite-calcite blebs in the facies, making it easily distinguishable from the CCMS.</i> - <i>GRADED LIMESTONE FACIES: Is a laminated argillaceous limestone with intercalated carbonaceous limestone laminae. The main rock type in the facies is laminated limestone with laminae up to 0.1-7mm thick.</i> - <i>LIGHT GREY BASAL LIMESTONE FACIES - LGLS: Consists of laminated argillaceous limestone. In the Anniv area it marks the end of the ACTM. It's not always present in the stratigraphy.</i> - <i>BASAL FACIES: This is a highly contorted and locally foliated carbonaceous mudstone. Unlike the other facies it is not repeated higher in the member. It appears locally to contain the slip zone of a major slump. The facies has only been observed in the YX area. It is 0.1-2m thick. The facies consists of massive carbonaceous siliceous mudstone with lenses and laminae of contorted, slightly carbonaceous chert.</i> « 9.10- 36.90 Fault zone-very carbonaceous, composed of calcareous mudstone and limestone as well as stuff so faulted it's unrecongnizable. Calcite veining through out and brecciated rock in many places. Pyrite masses with calcite also seen. No visible mineralization. Looks like ACTM for the most part. » « gg 30%» « bx 35%» « brco 20%» « 36.90- 38.10 Black, siliceous mudstone. Only pyrite and wispy			630133	45.10	45.80	0.70					
			630134	45.80	46.30	0.50					
			630135	46.30	47.20	0.90					
			630136	47.20	48.10	0.90					
			630137	48.10	48.70	0.60					
			630138	48.70	49.00	0.30					
			630139	49.00	49.50	0.50					
			630140	49.50	49.80	0.30					
			630141	49.50	49.80	0.30					
			630142	49.80	50.80	1.00					
			630143	50.80	51.60	0.80					
			630144	51.60	52.30	0.70					
			630145	52.30	52.70	0.40					
			630146	52.70	53.10	0.40					
			630147	53.10	54.10	1.00					
			630148	54.10	55.20	1.10					
			630149	55.20	55.70	0.50					
			630150	55.70	55.70	0.00					
			630151	55.70	56.00	0.30					
			630152	56.00	57.30	1.30					
			630153	57.30	57.80	0.50					
			630154	57.80	58.30	0.50					
			630155	58.30	59.90	1.60					
			630156	59.90	61.30	1.40					
			630157	61.30	62.40	1.10					
			630158	62.40	63.40	1.00					
			630159	63.40	64.20	0.80					
			630160	64.20	64.20	0.00					
			630161	64.20	65.50	1.30					
			630162	65.50	66.90	1.40					
			630163	66.90	67.80	0.90					
			630164	67.80	68.10	0.30					
			630165	68.10	69.50	1.40					

Selwyn Project Diamond Drill Log

Hole Number:
XYC-233

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		calcite laminae visible. No mineralization visible. »	630166	69.50	70.20	0.70					
		« 38.10- 38.60 Medium to dark grey laminated siliceous mudstone. Pyrite, calcite, quartz and/or galena, ~1-4cm thick, as well. »	630167	70.20	71.00	0.80					
		« 38.60- 39.40 Light grey, medium grained, massive limestone. Clast of laminated mudstone with galena surrounded by a pyrite and calcite vein ~10cm. »	630168	71.00	72.10	1.10					
		« 39.40- 41.10 Dark grey, finely laminated siliceous mudstone with a large proportion of pyrite and calcite veining up to 6cm thick. Some pyrite there looks laminate d. May be brecciated by calcite vein? Pyrite and sphalerite fine laminae, and very small galena stringers. Some calcareous layers as well (mud or limestone). Laminae are distorted. »	630169	72.10	73.50	1.40					
		« 41.10- 42.80 Medium grey, finely laminated, calcareous mudstone and limestone intercalated. Some sections show more pronounced laminations along with dewatering faults where coarse grained sphalerite, mudstone and/or galena was mobilized. These are likely higher grade areas and are distinguished by sampling intervals »	630170	73.50	74.90	1.40					
		« 42.80- 44.30 Light to medium grey, siliceous mudstone mangled with limestone. Laminations not present. "Wormy" calcite veins common. Galena blebs/stringers are rare but present. Coarse grained sphalerite and calcite veins also seen. »	630171	73.50	74.90	1.40					
		« 44.30- 46.30 Weakly calcareous to siliceous, laminated mudstone. Sections where laminae is wavy and block faulted. Galena and calcite blebs common there. Kind of carbonaceous. »	630172	74.90	76.00	1.10					
		« 46.30- 48.70 Light grey, massive to laminated, calcareous mudstone. Calcite stylolites. »	630173	76.00	77.40	1.40					
		« 48.70- 49.00 Medium grey, finely laminated, siliceous mudstone. Block faulted and coarse grained sphalerite following fault planes (water escape	630174	77.40	78.30	0.90					
			630175	78.30	78.90	0.60					
			630176	78.90	79.50	0.60					
			630177	79.50	80.00	0.50					
			630178	80.00	81.10	1.10					
			630179	81.10	81.40	0.30					
			630180	81.40	81.40	0.00					
			630181	81.40	82.80	1.40					
			630182	82.80	83.40	0.60					
			630183	83.40	84.20	0.80					
			630184	84.20	85.30	1.10					
			630185	85.30	87.00	1.70					
			630186	87.00	88.30	1.30					
			630187	88.30	89.80	1.50					
			630188	89.80	90.90	1.10					
			630189	90.90	92.30	1.40					
			630190	92.30	92.30	0.00					
			630191	92.30	93.90	1.60					
			630192	93.90	95.30	1.40					
			630193	95.30	96.90	1.60					
			630194	96.90	97.30	0.40					
			630195	97.30	99.60	2.30					
			630196	99.60	100.70	1.10					
			630197	100.70	101.00	0.30					
			630198	101.00	101.90	0.90					
			630199	101.90	102.10	0.20					
			630200	102.10	102.70	0.60					

Selwyn Project Diamond Drill Log

Hole Number:
XYC-233

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		structures). »	630201	102.10	102.70	0.60					
		« 49.00- 49.50 Dark grey, weakly calcareous, laminated mudstone with light grey limestone. Galena blebs/stringers visible in mudstone, not common. Calcite veins up to 3cm visible. »	630202	102.70	103.60	0.90					
			630203	103.60	104.40	0.80					
			630204	104.40	105.40	1.00					
			630205	105.40	106.10	0.70					
			630206	106.10	106.90	0.80					
		« 49.50- 49.80 Light grey, graded limestone. »	630207	106.90	107.50	0.60					
			630208	107.50	107.90	0.40					
		« 49.80- 51.60 Light to dark grey, laminated, weakly calcareous, metalliferous, mangled mudstone and limestone. Smeared limestone clasts present. Parts are high grade. »	630209	107.90	109.30	1.40					
			630210	109.30	109.30	0.00					
			630211	109.30	110.10	0.80					
			630212	110.10	111.00	0.90					
		« 51.60- 52.30 Medium grey, laminated, metalliferous mudstone. High grade. Fine and coarse grained galena and fine grained sphalerite veins. Numerous calcite stringers and blebs. »	630213	111.00	112.50	1.50					
			630214	112.50	114.00	1.50					
			630215	114.00	115.20	1.20					
			630216	115.20	116.40	1.20					
		« 52.30- 52.70 Medium to dark grey, calcareous mudstone mangled with limestone and calcite veins. Rare galena stringers and coarse grained sphalerite. »	630217	116.40	117.50	1.10					
			630218	117.50	118.40	0.90					
			630219	118.40	118.80	0.40					
			630220	118.80	118.80	0.00					
		« 52.70- 53.10 Light grey limestone, faint graded beds visible. No visible mineralization. »	630221	118.80	120.00	1.20					
			630222	120.00	120.70	0.70					
			630223	120.70	122.20	1.50					
		« 53.10- 55.70 Medium grey, laminated, calcareous mudstone with smeared limestone clasts. Laminae are kink folded with mud and/or fine grained galena infilling faults. Galena disseminated in some limestone clasts as well. Pyrite and calcite also seen in veins, mud stylolites also present. »	630224	122.20	123.30	1.10					
			630225	123.30	124.10	0.80					
			630226	124.10	124.70	0.60					
			630227	124.70	125.80	1.10					
			630228	125.80	126.10	0.30					
		« 55.70- 56.00 A layer of high grade, light grey, laminated, weakly calcareous, metalliferous mudstone. Fine grained galena infilling fractures. »	630229	126.10	126.30	0.20					
			630230	126.30	126.60	0.30					
			630231	126.60	126.60	0.00					
			630232	126.60	127.40	0.80					
		« 56.00- 57.30 Light grey, laminated, calcareous mudstone. Calcite stylolites and veins common, Smeared limestone clasts present. »	630233	127.40	127.70	0.30					
			630234	127.70	128.30	0.60					
			630235	128.30	129.00	0.70					

Selwyn Project Diamond Drill Log

Hole Number:
XYC-233

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
« 57.30- 57.80 Light grey, muddy limestone. » « 57.80- 58.30 Medium grey, laminated, calcareous mudstone and light grey smeared limestone clasts. » « 58.30- 62.40 Light grey, muddy limestone. Pyrite and calcite bleb at 60.4m. » « 62.40- 64.20 Fault-black, siliceous and carbonaceous, monotonous mudstone. First 10cm is brecciated by calcite veins. » « gg 10% » « bx 70% » « brco 15% » « 64.20- 66.90 Black, siliceous mudstone with areas of weakly calcareous mudstone. Faintly laminated but difficult to see. Very heavily fractures, carbonaceous as we ll. » « 66.90- 67.80 Medium to dark grey, calcareous mudstone and limestone. Pyrite and calcite veins. » « 67.80- 71.00 Light grey, muddy limestone. Stylolites of mudstone and calcite. Also have euhedral calcite filled veins/fractures. Pyrite also common. » « 71.00- 72.10 Medium grey, calcareous mudstone. Carbonaceous. Calcite veining present. Numerous parallel healed fractures. » « 72.10- 78.30 Medium to light grey, laminated, siliceous to weakly calcareous limestone. Laminae are extensively faulted. Fine grained galena and/or sphalerite visible on fault planes. Limestone clasts towards end of interval up to 25cm wide and some coarse grained galena mineralization on edges of clasts. Low to high grade. » « 78.00- 78.30 Fault » « gg 10% » « bx 90% » « 78.30- 78.90 Limestone with calcite veins up to 4cm thick (most			630236	129.00	129.10	0.10					
			630237	129.10	129.40	0.30					
			630238	129.40	130.90	1.50					
			630239	130.90	131.90	1.00					
			630240	131.90	131.90	0.00					
			630241	131.90	133.10	1.20					
			630242	133.10	133.30	0.20					
			630243	133.30	133.80	0.50					
			630244	133.80	134.20	0.40					
			630245	134.20	134.80	0.60					
			630246	134.80	136.20	1.40					
			630247	136.20	137.00	0.80					
			630248	137.00	137.70	0.70					
			630249	137.70	138.70	1.00					
			630250	138.70	138.70	0.00					
			630251	138.70	139.50	0.80					
			630252	139.50	140.70	1.20					
			630253	140.70	141.30	0.60					
			630254	141.30	141.90	0.60					
			630255	141.90	142.00	0.10					
			630256	142.00	142.80	0.80					
			630257	142.80	142.90	0.10					
			630258	142.90	144.20	1.30					
			630259	144.20	145.60	1.40					
			630260	145.60	146.70	1.10					
			630261	145.60	146.70	1.10					
			630262	146.70	147.00	0.30					
			630263	147.00	147.00	0.00					
			630264	147.00	148.50	1.50					
			630265	148.50	149.80	1.30					
			630266	149.80	151.00	1.20					
			630267	151.00	152.10	1.10					
			630268	152.10	153.30	1.20					
			630269	153.30	154.70	1.40					
			630270	154.70	154.70	0.00					

Selwyn Project Diamond Drill Log

Hole Number:
XYC-233

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
~1mm). No mineralization visible. »			630271	154.70	155.30	0.60					
« 78.90- 79.50 Calcite brecciated limestone or calcareous mudstone. Very carbonaceous. Pyrite with calcite as well. »			630272	155.30	157.10	1.80					
			630273	157.10	157.60	0.50					
			630274	157.60	157.80	0.20					
« 79.50- 80.00 Medium grey, calcareous mudstone. Calcite and pyrite blebs. Carbonaceous. »			630275	157.80	159.20	1.40					
			630276	159.20	159.90	0.70					
			630277	159.90	160.60	0.70					
			630278	160.60	161.90	1.30					
« 80.00- 81.10 Fault-black, weakly calcareous , carbonaceous mudstone. Pyrite and calcite veins. » « gg 20%» « bx 50%» « brco 30%»			630279	161.90	162.50	0.60					
			630280	162.50	162.50	0.00					
			630281	162.50	162.80	0.30					
« 81.10- 81.40 Medium grey, limestone and mudstone laminae intermixed. Pyrite laminae as well as blebs (with calcite). »			630282	162.80	164.20	1.40					
			630283	164.20	164.40	0.20					
			630284	164.40	165.50	1.10					
« 81.40- 82.80 Medium to light grey, muddy limestone. Pyrite laminae and rare mudstone laminae present. »			630285	165.50	165.90	0.40					
			630286	165.90	166.80	0.90					
			630287	166.80	168.20	1.40					
« 82.80- 83.40 Light grey, calcareous mudstone and limestone layers. Calcite veining also common. Limestone clasts as well. »			630288	168.20	169.80	1.60					
			630289	169.80	170.90	1.10					
			630290	170.90	171.70	0.80					
« 83.40- 84.20 Light grey graded to massive limestone. »			630291	170.90	171.70	0.80					
			630292	171.70	172.60	0.90					
« 84.20- 92.30 Medium to dark grey, laminated, calcareous mudstone. Laminae are almost 0 degrees tca. Calcite stylolites and pyrite blebs with calcite common. Lamina e are faulted in areas and filled by calcite/mudstone predominantly. Possible sphalerite laminae (very fine grained). »			630293	172.60	173.90	1.30					
			630294	173.90	175.40	1.50					
			630295	175.40	176.80	1.40					
			630296	176.80	178.30	1.50					
			630297	178.30	179.00	0.70					
« 92.30- 100.70 Medium to dark grey, laminated in places, mudstone. Alternates from siliceous to calcareous, probably due to disseminated calcite content. Weak to no mineralization. »			630298	179.00	180.10	1.10					
			630299	180.10	181.00	0.90					
			630300	181.00	181.00	0.00					
			630301	181.00	181.70	0.70					
« 100.70- 101.00 Light grey, graded limestone. »			630302	181.70	182.20	0.50					
			630303	182.20	183.50	1.30					
« 101.00- 101.90 Dark grey to black, calcareous and siliceous mudstone. » « gg 10%» « bx 40% »			630304	183.50	184.50	1.00					
			630305	184.50	185.30	0.80					

Selwyn Project Diamond Drill Log

Hole Number:
XYC-233

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
« 101.90- 102.10 Light grey limestone. » « 102.10- 102.70 Fault-black, siliceous mudstone with an ~10cm clast of limestone. » « gg 10% » « bx 25% » « 102.70- 104.40 Light grey, graded limestone with some mudstone laminae. » « 104.40- 106.10 Fault-black, siliceous, carbonaceous mudstone. Healed fractures (carbonaceous) common. Laminations not visible. Calcite veins up to 5mm thick. » « gg 10% » « bx 50% » « brco 30% » « 106.10- 106.90 Light grey, graded limestone intercalated with black siliceous mudstone. Some disseminated pyrite in limestone. » « 106.90- 107.90 Medium to dark grey laminated to massive siliceous mudstone. No visible mineralization. » « 107.90- 109.30 Medium grey, muddy limestone. No visible mineralization. » « 109.30- 111.00 Dark grey, laminated, calcareous mudstone. Laminae and calcite veins are distorted in the most part. Calcite veinlets (spider web-like) as well as sty lolites seen. Pyrite and calcite also present. » « 111.00- 112.50 Medium grey layered minestone and calcareous mudstone. Calcite stylolites present. Laminae are folded/smeared. » « 112.50- 114.00 Dark grey, laminated in places. calcareous mudstone. Lots of disseminated calcite and parallel, planer calcite veins. » « 114.00- 117.50 Light to medium grey graded limestone mangled with dark grey mudstone and pyrite-calcite veins. Extensive calcite veins in all orientations. Carbonace ous. »			630306	185.30	186.80	1.50					
			630307	186.80	188.20	1.40					
			630308	188.20	189.40	1.20					
			630309	189.40	189.60	0.20					
			630310	189.60	189.60	0.00					
			630311	189.60	189.80	0.20					
			630312	189.80	190.30	0.50					
			630313	190.30	190.80	0.50					
			630314	190.80	191.70	0.90					
			630315	191.70	192.30	0.60					
			630316	192.30	193.60	1.30					
			630317	193.60	194.30	0.70					
			630318	194.30	195.00	0.70					
			630319	195.00	196.30	1.30					
			630320	196.30	196.70	0.40					
			630321	196.30	196.70	0.40					
			630322	196.70	197.30	0.60					
			630323	197.30	198.40	1.10					
			630324	198.40	199.30	0.90					
			630325	199.30	200.40	1.10					
			630326	200.40	200.90	0.50					
			630327	200.90	202.20	1.30					
			630328	202.20	203.30	1.10					
			630329	203.30	204.80	1.50					
			630330	204.80	204.80	0.00					
			630331	204.80	206.30	1.50					
			630332	206.30	207.00	0.70					
			630333	207.00	207.50	0.50					
			630334	207.50	208.10	0.60					
			630335	208.10	209.20	1.10					
			630336	209.20	210.50	1.30					
			630337	210.50	210.90	0.40					
			630338	210.90	211.60	0.70					
			630339	211.60	213.10	1.50					
			630340	213.10	213.10	0.00					

Selwyn Project Diamond Drill Log

Hole Number:
XYC-233

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
« 117.50- 118.40 Dark grey, siliceous, carbonaceous mudstone. Laminations not visible, there are lots of healed fractures however. » « 118.40- 118.80 Light grey limestone clast. » « 118.80- 120.00 Dark to medium grey, siliceous mudstone with some lighter chert layers. Calcite stylolites present. No mineralization visible. » « 120.00- 120.70 Light grey limestone with extensive calcite veining and some dark grey mudstone. » « 120.70- 124.10 Dark grey to black, mostly massive, siliceous, carbonaceous mudstone. Some chert-like banding visible. Can't see any mineralization. » « 124.10- 124.70 Medium to dark grey, laminated, siliceous, metalliferous mudstone. Laminae are planer to distorted (by faulting/folding). Pyrite common. Sphalerite l aminations fine grained. Fine grained galena veinlets. » « 124.70- 125.80 Medium to dark grey breccia composed of laminated siliceous mudstone (similar to previous interval), pyrite agglomerates, calcite veins. Mud matrix. P ost brecciation calcite veins as well. » « 125.80- 126.10 Medium grey limestone concretion. » « 126.10- 126.30 Dark grey, laminated, siliceous mudstone. Sphalerite laminae possible. » « 126.30- 126.60 Light grey limestone concretion with pyrite and calcite veining. » « 126.60- 127.40 Weakly to moderately calcareous, laminated mudstone and smeared limestone. Fine grained sphalerite laminations. »			630341	213.10	214.50	1.40					
			630342	214.50	216.00	1.50					
			630343	216.00	217.50	1.50					
			630344	217.50	218.90	1.40					
			630345	218.90	219.70	0.80					
			630346	219.70	221.20	1.50					
			630347	221.20	222.00	0.80					
			630348	222.00	223.50	1.50					
			630349	223.50	224.80	1.30					
			630350	224.80	226.30	1.50					
			630351	224.80	226.30	1.50					
			630352	226.30	227.00	0.70					
			630353	227.00	228.00	1.00					
			630354	228.00	229.30	1.30					
			630355	229.30	230.80	1.50					
			630356	230.80	231.70	0.90					
			630357	231.70	233.20	1.50					
			630358	233.20	234.10	0.90					
			630359	234.10	235.30	1.20					
			630360	235.30	235.30	0.00					
			630361	235.30	236.10	0.80					
			630362	236.10	236.60	0.50					
			630363	236.60	237.80	1.20					
			630364	237.80	238.90	1.10					
			630365	238.90	239.60	0.70					
			630366	239.60	240.70	1.10					
			630367	240.70	241.40	0.70					
			630368	241.40	242.90	1.50					
			630369	242.90	243.90	1.00					
			630370	243.90	243.90	0.00					
			630371	243.90	245.20	1.30					
			630372	245.20	246.70	1.50					
			630373	246.70	248.20	1.50					
			630374	248.20	248.90	0.70					
			630375	248.90	249.30	0.40					

Selwyn Project Diamond Drill Log

Hole Number:
XYC-233

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		« 127.40- 127.70 Medium grey, massive, siliceous mudstone. Fine grained galena mineralization in healed fracture planes. Coarse grained galena present as well. Some lam inated mudstone (breccia pieces?) present. »	630376	249.30	250.80	1.50					
			630377	250.80	252.30	1.50					
			630378	252.30	253.50	1.20					
			630379	253.50	254.10	0.60					
		« 127.70- 128.30 Dark grey, siliceous mudstone, but mostly a large calcite and pyrite vein. »									
		« 128.30- 129.00 Medium to dark grey, brecciated, siliceous mudstone, some limestone and pyrite-calcite veins. Fine grained galena veins. »									
		« 129.00- 129.10 Light grey limestone. »									
		« 129.10- 129.40 Dark grey, siliceous mudstone and limestone breccia. Calcite and pyrite veins. Fine and coarse grained galena veins. »									
		« 129.40- 130.90 Dark grey, laminated, siliceous mudstone with limestone clasts and a ~17cm thick pyrite and calcite vein. »									
		« 130.90- 131.90 Light to medium grey, laminated, siliceous mudstone, limestone breccia. Mudstone laminae are faulted. »									
		« 131.90- 133.10 Medium grey, laminated, siliceous mudstone with a couple limestone layers (<1cm thick). Healed fractures faulting laminae are present. »									
		« 133.10- 133.30 Light grey limestone. »									
		« 133.30- 133.80 Dark grey, laminated, calcareous mudstone. Laminae are faulted. »									
		« 133.80- 134.20 Light grey limestone. No visible mineralization. »									
		« 134.20- 137.70 Light to medium grey, calcareous, laminated mudstone mangled with light grey limestone. Calcite laminae and veining throughout. No									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-233

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		visible mineralizat ion. »									
		« 137.70- 139.50 Dark grey to black, siliceous, laminated in places, carbonaceous mudstone. Some limestone clasts as well. »									
		« 139.00- 139.20 Fault » « gg 5%» « bx 55%» « brco 40%»									
		« 139.50- 140.70 Light grey limestone and dark grey, siliceous mudstone breccia. Coarse grained galena seen. »									
		« 140.70- 141.90 Medium to dark grey, siliceous mudstone. High grade in places. Fine grained sphalerite and galena. Pyrite and calcite vein as well. »									
		« 141.90- 142.00 Light grey limestone and calcite vein. »									
		« 142.00- 142.80 Dark grey, siliceous mudstone, laminated. High grade. Fine grained galena veins following faults. »									
		« 142.80- 142.90 Light grey, graded limestone. »									
		« 142.90- 146.70 Black, carbonaceous, siliceous mudstone. No mineralization visible. Calcite wormy veins. »									
		« 143.80- 144.00 Fault » « gg 30%» « bx 70%»									
		« 146.70- 153.30 Light to dark grey, siliceous, laminated mudstone. Coarse grained galena visible. Pyrite and calcite common. Laminations are very low angle. »									
		« 153.30- 154.70 Black, siliceous mudstone that looks alot like USMS. Lighter grey chert bands and numerous calcite veins. Carbonaceous. »									
		« 154.70- 155.30 Light grey, coarse grained, graded limestone. Calcite veins up to 10cm wide. »									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-233

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		« 155.30- 157.10 Black, USMS like rock. Very fractured. »									
		« 157.10- 157.60 Light grey limestone concretion and calcite veins. »									
		« 157.60- 157.80 Black USMS like rock. »									
		« 157.80- 159.20 Light grey, recrystallized limestone with a ~3cm thick quartz-calcite vein, ~0 degrees tca. »									
		« 159.20- 159.90 Black, USMS like, siliceous mudstone with wormy chert bands. It looks as if this is USMS with limestone clasts as typical. Perhaps due to the very low angle of drilling to bedding we are close to the upper ACTM/USMS contact and weaving in and out? Will sample as ACTM because of trace mineralization. »									
		« 159.90- 160.60 Medium to light grey graded limestone. Partially recrystallized. »									
		« 160.60- 161.90 Black, USMS-like siliceous mudstone. »									
		« 161.90- 162.50 Light grey, recrystallized limestone. »									
		« 162.50- 162.80 Black, USMS-like, siliceous, cherty mudstone. »									
		« 162.80- 164.20 Black, USMS-like mudstone and light grey limestone clasts/concretions. No visible mineralization. »									
		« 164.20- 164.40 Black, USMS-like mudstone. »									
		« 164.40- 166.80 Light to medium grey, graded limestone. Some black mudstone sections/laminae. Quartz and calcite veining common. »									
		« 166.80- 171.70 Black, siliceous, carbonaceous, USMS-like mudstone with chert bands. No visible mineralization. »									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-233

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		« 171.70- 172.60 Light grey limestone. »									
		« 172.60- 179.00 Black, USMS-like, siliceous, carbonaceous mudstone. No visible mineralization. »									
		« 179.00- 181.00 ACTM. Dark grey-yellow laminated, siliceous mudstone and sections of brecciated mudstone with calcite and pyrite veining. Limestone clasts (frequently rimmed in pyrite). Fine grained sphalerite laminae visible. »									
		« 181.00- 181.70 Light grey limestone mangled with laminae and dark grey calcareous mudstone. Coarse grained galena vein near bottom contact. »									
		« 181.70- 183.50 Breccia composed of siliceous laminated mudstone, calcareous mudstone, limestone and intense calcite and quartz veining. Light to medium grey. No visible mineralization. Also see pyrite and calcite veins. »									
		« 183.50- 184.50 Dark grey, laminated, siliceous mudstone. Laminae range from planar to heavily offset by healed microfaults. Pyrite and sphalerite laminae present. »									
		« 184.50- 185.30 Light grey, siliceous, metalliferous, laminated mudstone. High grade. Fine and coarse grained galena veins (parallel) ~2mm thick. Pyrite and calcite veins common. Coarse grained sphalerite and calcite veins. Mineralized veins are offsetting laminae (block faulting). »									
		« 185.30- 189.60 Medium to dark grey, laminated, siliceous mudstone. Laminae are offset by microfaults. Coarse grained galena stringers present. Low to medium grade. »									
		« 189.60- 189.80 Light grey limestone (?), heavily veined by calcite. »									
		« 189.80- 190.30 Light grey, massive limestone. »									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-233

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		« 190.30- 190.80 Dark grey, faintly laminated in places, calcareous mudstone. Fractured. »									
		« 190.80- 191.70 Medium grey limestone, calcareous mudstone and siliceous mudstone all mangled together. Fractured. »									
		« 191.70- 192.30 Light grey limestone. Veined by calcite. »									
		« 192.30- 194.30 Medium to dark grey, massive to laminated, weakly calcareous mudstone. Laminae are microfaulted in places. Many have fractures. Some limestone clasts as well. »									
		« 194.30- 195.00 Black, massive, siliceous mudstone with rare limestone clasts. Calcite stringers and veins common. »									
		« 195.00- 196.30 Medium grey, thinly laminated, siliceous mudstone with pyrite bands and nodules, locally limestone nodules are seen. »									
		« 196.30- 196.70 Light grey limestone concretion. »									
		« 196.70- 197.30 Medium grey, thinly laminated, siliceous mudstone. Low grade. »									
		« 197.30- 199.30 Light grey limestone. »									
		« 199.30- 200.40 High grade. Medium grey mudstone. »									
		« 200.40- 202.20 Medium grey, thinly laminated, siliceous mudstone with local limestone nodules in various shapes and sizes. Galena blebs are seen locally, low to medium grade. »									
		« 202.20- 203.30 Medium grey, thinly laminated, calcareous mudstone with local limestone nodules. Low to moderate grade. »									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-233

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		« 203.30- 207.00 Light grey limestone. Quartz veining is well developed. »									
		« 207.00- 207.50 Dark grey, siliceous mudstone with thin laminae. Moderate grade. »									
		« 207.50- 208.10 Light grey limestone. »									
		« 208.10- 209.20 Medium grey, siliceous mudstone with thin laminae. Low grade. »									
		« 209.20- 210.90 Light grey limestone. »									
		« 210.90- 214.50 Dark grey, siliceous mudstone with thin laminae. Low to moderate grade. »									
		« 214.50- 218.90 Black, siliceous mudstone. »									
		« 218.90- 219.70 Dark grey, siliceous mudstone with thin laminae. Low grade. »									
		« 219.70- 222.00 Light to medium grey, siliceous mudstone with low grades. »									
		« 222.00- 224.80 Dark grey, siliceous mudstone with low grades. »									
		« 224.80- 226.30 Light grey mudstone. Barren. »									
		« 226.30- 227.00 Light grey limestone. »									
		« 227.00- 228.00 High grade. Light grey, calcareous mudstone. »									
		« 228.00- 229.30 Light grey limestone. »									
		« 229.30- 231.70 Light grey, siliceous mudstone. Barren. »									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-233

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
« 231.70- 234.10 Black, siliceous mudstone. Barren. »											
« 234.10- 236.10 Light grey limestone with dark grey sections. »											
« 236.10- 237.80 High grade. Light-medium grey mudstone. »											
« 237.80- 238.90 Medium grey, siliceous mudstone with moderate grades. »											
« 238.90- 239.60 Whitish grey, siliceous mudstone with high grades. »											
« 239.60- 241.40 Light grey limestone. »											
« 241.40- 243.90 Medium to dark grey, siliceous mudstone with thin laminae. Moderate grade. »											
« 243.90- 245.20 Light-medium grey, calcareous mudstone with low grades. »											
« 245.20- 248.20 Light-medium grey, siliceous mudstone with low grades. »											
« 248.20- 249.30 Light grey, calcareous mudstone with low to moderate grades. »											
« 249.30- 254.10 Light grey limestone. »											
254.10	258.40	FLT	630380	254.10	254.70	0.60					
Whole core is black siliceous mudstone.			630381	254.10	254.70	0.60					
« 254.10- 258.40 Fault » « gg 15% » « bx 30% » « brco 40% »			630382	254.70	255.40	0.70					
258.40	336.80	USMS	630383	334.80	335.80	1.00					
USMS – Upper Siliceous Mudstone			630384	335.80	336.80	1.00					
Consists of interlaminated dark grey to black mudstone and light to medium grey chert. Regionally, a 1m thick graptolite zone occurs 15m below the top of the											

Selwyn Project Diamond Drill Log

Hole Number:
XYC-233

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		upper unit, this is usable as a horizon. The USMS is divided into 3 units. The Lower Unit contains abundant limestone concretions and Galena and sphalerite micro-concretions occur locally near the base of this unit. « gra , lm chrt -20.00% », « cg xtl sph crns ca 5.00-20.00cm », « bed chrt 10.00-15.00% », Black, carbon rich, siliceous mudstone with wormy, medium grey chert bands. « 276.80- 279.10 Fault-whole core is black mudstone with limestone clasts. » « gg 5%» « bx 15%» « brco 60%» « 287.10- 291.00 Fault » « gg 15%» « bx 15%» « brco 60%» « 301.40- 331.50 Fault » « gg 10%» « bx 20%» « brco 50%» « 331.50- 336.80 Light grey limestone (maybe basal limestone in ACTM), 20cm of fault gouge in lower contact. »									
336.80	357.60	ACTM	630385	336.80	337.80	1.00					
		ACTM – Active Member	630386	337.80	339.10	1.30					
		The ACTM consists of a repetitive, possibly rhythmic, sequence of intercalated carbonaceous mudstone, cherty mudstone, chert and limestone and locally contains economically significant Zn and Pb sulphides (see bold marked facies), mainly in its sections with well developed lamination. Because of its heterogeneity, the member is distinctive and easily identified.	630387	339.10	340.50	1.40					
		=====	630388	340.50	341.00	0.50					
		The ACTM has 8 different facies:	630389	341.00	342.50	1.50					
		=====	630390	342.50	342.50	0.00					
		- GREY CHERT FACIES: Consists of laminated medium light grey to medium dark grey chert. Mineralization: 95-99% quartz and up to 5% secondary calcite.	630391	342.50	344.00	1.50					
			630392	344.00	344.40	0.40					
			630393	344.40	345.90	1.50					
			630394	345.90	347.30	1.40					
			630395	347.30	347.70	0.40					
			630396	347.70	349.20	1.50					
			630397	349.20	350.70	1.50					
			630398	350.70	351.60	0.90					
			630399	351.60	353.10	1.50					
			630400	353.10	353.10	0.00					
		- WHITISH GREY ZN-PB MUDSTONE FACIES: Is a laminated cherty rock containing up	630401	353.10	354.60	1.50					

Selwyn Project Diamond Drill Log

Hole Number:
XYC-233

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		to 70% sulphides. Mineralization: quartz, sphalerite and galena are the major minerals with only minor amounts of pyrite and locally calcite. Sedimentary diagenetic structures are common and well displayed in the facies, such as: lamination, pseudo-beds, calcite nodules & limestone nodules and abundant water escape structures. Most obvious structure in facies is cross-cutting veins containing massive sphalerite and galena with minor pyrite. They range in width from 0.5 to 10mm. - THIN BEDDED CHERTY MUDSTONE FACIES: Consists of rhythmic intercalated laminae of chert, carbonaceous mudstone and minor micrite. This facies contains significant amounts of Zn and Pb sulphides. - CHERTY MUDSTONE FACIES: Consists of a greyish black monotonous siliceous, carbonaceous mudstone. It is most typically found overlying the thin bedded calcareous mudstone facies. - THIN BEDDED CALCAREOUS MUDSTONE FACIES: Consists of laminated carbonaceous mudstone containing 20-40% calcite, 40-55% quartz and 10-20% muscovite. Sulphides occur in laminae. In the XY area it is usually the lowest facies in the section to contain laminated sulphides. - CALCAREOUS MUDSTONE FACIES: Consists of grey to greyish black monotonous, calcareous siliceous carbonaceous mudstone. There are no feathery calcite beds or pyrite-calcite blebs in the facies, making it easily distinguishable from the CCMS. - GRADED LIMESTONE FACIES: Is a laminated argillaceous limestone with intercalated carbonaceous limestone laminae. The main rock type in the facies is laminated limestone with laminae up to 0.1-7mm thick. - LIGHT GREY BASAL LIMESTONE FACIES - LGLS: Consists of laminated argillaceous limestone. In the Anniv area it marks the end of the ACTM. It's not always present in the stratigraphy.	630402	354.60	356.10	1.50					
			630403	356.10	357.60	1.50					

Selwyn Project Diamond Drill Log

Hole Number:
XYC-233

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
- BASAL FACIES: This is a highly contorted and locally foliated carbonaceous mudstone. Unlike the other facies it is not repeated higher in the member. It appears locally to contain the slip zone of a major slump. The facies has only been observed in the YX area. It is 0.1-2m thick. The facies consists of massive carbonaceous siliceous mudstone with lenses and laminae of contorted, slightly carbonaceous chert. « 336.80- 337.80 Dark grey, siliceous mudstone with thin laminae locally. Low grade. » « 337.80- 339.10 Light grey limestone. » « 339.10- 340.50 Dark grey siliceous mudstone with low grades. » « 340.50- 341.00 Light grey limestone. » « 341.00- 342.50 Dark grey siliceous mudstone with thin laminae and limestone nodules. Low grade. » « 342.50- 344.40 Medium grey limestone. » « 344.40- 345.90 Fault-broken pieces are black mudstone. » « gg 20%» « bx 50%» « brco 30%» « 345.90- 347.70 Medium grey limestone » « 347.70- 351.60 Medium grey siliceous mudstone with low grade. » « 351.60- 359.60 Light grey limestone. » « 359.60- 357.60 Fault-whole core is black calcareous mudstone. » « gg 10%» « bx 30%» « brco 50%»											
357.60	382.80	FLT	630404	357.60	358.40	0.80					
			630405	358.40	359.20	0.80					

Selwyn Project Diamond Drill Log

Hole Number:
XYC-233

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		« 357.60- 382.80 Fault-whole core is black calcareous mudstone » « gg 10%» « bx 30%» « brco 50%»									
382.80	536.30	CCMS									
CCMS – Calcareous Mudstone											
Massive, calcareous, carbonaceous, dark grey mudstone. Most of the member is massive, but rare poorly defined bedding and pyrite-calcite micro-concretions are present. Most diagnostic structures are feathery calcite beds (=thin calcite-cemented concretions, many of them contain pyrite cores) and calcite pseudo-beds (= fibrous calcite vein parallel to bedding).											
« lm ca 5.00-10.00mm », « nodules py -3.00% 2.00-20.00mm », Black calcareous mudstone with faint very fine grained pyrite beds, some sections look like Backside (dark grey colour and squiggly bands).											
« 410.60- 430.70 Fault-whole core is black calcareous mudstone. » « gg 10%» « bx 10%» « brco 50%» « 430.70- 441.90 Black calcareous mudstone, sections of grey limestone nodules locally are seen. » « 441.90- 445.90 Fault-broken core is black calcareous mudstone and limestone clasts. » « gg 10%» « bx 30%» « brco 60%» « 445.90- 480.60 Black calcareous mudstone » « 480.60- 499.00 Fault-whole core is black calcareous mudstone » « gg 10%» « bx 10%» « brco 60%» « 499.00- 536.30 Black calcareous mudstone »											
536.30	578.50	FLT									
« 536.30- 578.50 Fault » « gg 5%» « bx 10%» « brco 45%»											

Selwyn Project Diamond Drill Log

Hole Number:
XYC-233

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		Whole core is black calcareous mudstone, black siliceous mudstone, limestone nodules and clast-supported breccia. Mixture of ccms and bssm?									
578.50	630.10	FLMD FLMD – Flaggy Mudstone Formation Dark grey mudstone in the upper portions of the unit grading into light grey mudstone to siltstone. Contains abundant wispy bioturbation which ranges from randomly-oriented at the top of the unit to bedding-parallel throughout the majority of the unit. Darker upper section has a strong fetid odour along broken surfaces. « btrb 0.10-2.00cm », « cg xtl crns ca 1.00-5.00% 5.00-150.00cm », « crns py 1.00-5.00% 0.10-0.50mm », Light-medium grey siliceous mudstone with black stretches. Locally dark grey siliceous mudstone bands are seen. No apparent orientation for black stretches.									
630.10	663.00	USMS USMS – Upper Siliceous Mudstone Consists of interlaminated dark grey to black mudstone and light to medium grey chert. Regionally, a 1m thick graptolite zone occurs 15m below the top of the upper unit, this is usable as a horizon. The USMS is divided into 3 units. The Lower Unit contains abundant limestone concretions and Galena and sphalerite micro-concretions occur locally near the base of this unit. « gra , lm chrt -20.00% », « cg xtl sph crns ca 5.00-20.00cm », « bed chrt 10.00-15.00% », Black carbonaceous siliceous mudstone with medium grey wavy chert bands. All the section is quite broken. Core >10cm is ~50%.	630406	660.50	662.00	1.50					
			630407	662.00	663.00	1.00					
663.00	695.20	ACTM ACTM – Active Member The ACTM consists of a repetitive, possibly rhythmic, sequence of intercalated carbonaceous mudstone, cherty mudstone, chert and limestone and locally contains economically significant Zn and Pb sulphides (see bold marked facies), mainly in its sections with well developed lamination. Because of its	630408	663.00	663.70	0.70					
			630409	663.70	664.10	0.40					
			630410	664.10	665.10	1.00					
			630411	664.10	665.10	1.00					
			630412	665.10	666.60	1.50					
			630413	666.60	667.40	0.80					
			630414	667.40	668.90	1.50					

Selwyn Project Diamond Drill Log

Hole Number:
XYC-233

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		heterogeneity, the member is distinctive and easily identified.	630415	668.90	670.10	1.20					
		=====	630416	670.10	670.80	0.70					
		The ACTM has 8 different facies:	630417	670.80	671.50	0.70					
		=====	630418	671.50	672.90	1.40					
		- GREY CHERT FACIES: Consists of laminated medium light grey to medium dark grey chert. Mineralization: 95-99% quartz and up to 5% secondary calcite.	630419	672.90	674.00	1.10					
			630420	674.00	674.00	0.00					
		- WHITISH GREY ZN-PB MUDSTONE FACIES: Is a laminated cherty rock containing up to 70% sulphides. Mineralization: quartz, sphalerite and galena are the major minerals with only minor amounts of pyrite and locally calcite. Sedimentary diagenetic structures are common and well displayed in the facies, such as: lamination, pseudo-beds, calcite nodules & limestone nodules and abundant water escape structures. Most obvious structure in facies is cross-cutting veins containing massive sphalerite and galena with minor pyrite. They range in width from 0.5 to 10mm.	630421	674.00	675.50	1.50					
			630422	675.50	677.00	1.50					
			630423	677.00	678.40	1.40					
			630424	678.40	679.90	1.50					
			630425	679.90	681.10	1.20					
			630426	681.10	682.30	1.20					
			630427	682.30	683.80	1.50					
			630428	683.80	685.30	1.50					
			630429	685.30	686.80	1.50					
			630430	686.80	686.80	0.00					
			630431	686.80	687.10	0.30					
			630432	687.10	688.60	1.50					
			630433	688.60	690.10	1.50					
			630434	690.10	691.60	1.50					
			630435	691.60	693.10	1.50					
			630436	693.10	694.00	0.90					
			630437	694.00	695.20	1.20					
		- THIN BEDDED CHERTY MUDSTONE FACIES: Consists of rhythmic intercalated laminae of chert, carbonaceous mudstone and minor micrite. This facies contains significant amounts of Zn and Pb sulphides.									
		- CHERTY MUDSTONE FACIES: Consists of a greyish black monotonous siliceous, carbonaceous mudstone. It is most typically found overlying the thin bedded calcareous mudstone facies.									
		- THIN BEDDED CALCAREOUS MUDSTONE FACIES: Consists of laminated carbonaceous mudstone containing 20-40% calcite, 40-55% quartz and 10-20% muscovite. Sulphides occur in laminae. In the XY area it is usually the lowest facies in the section to contain laminated sulphides.									
		- CALCAREOUS MUDSTONE FACIES: Consists of grey to greyish black monotonous, calcareous siliceous carbonaceous mudstone. There are no feathery calcite beds									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-233

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		or pyrite-calcite blebs in the facies, making it easily distinguishable from the CCMS. - GRADED LIMESTONE FACIES: Is a laminated argillaceous limestone with intercalated carbonaceous limestone laminae. The main rock type in the facies is laminated limestone with laminae up to 0.1-7mm thick. - LIGHT GREY BASAL LIMESTONE FACIES - LGLS: Consists of laminated argillaceous limestone. In the Anniv area it marks the end of the ACTM. It's not always present in the stratigraphy. - BASAL FACIES: This is a highly contorted and locally foliated carbonaceous mudstone. Unlike the other facies it is not repeated higher in the member. It appears locally to contain the slip zone of a major slump. The facies has only been observed in the YX area. It is 0.1-2m thick. The facies consists of massive carbonaceous siliceous mudstone with lenses and laminae of contorted, slightly carbonaceous chert. « 663.00- 663.70 Medium grey siliceous mudstone with thin laminae. Low grade. » « 663.70- 664.10 High grade, light grey mudstone. » « 664.10- 667.40 Light grey calcareous mudstone with moderate grades locally. » « 667.40- 671.50 Medium grey siliceous mudstone with thin laminae. Moderate grade. » « 671.50- 674.00 Light grey limestone. » « 674.00- 678.40 Medium grey siliceous mudstone with thin laminae. Low grade. »									

Selwyn Project

Diamond Drill Log

Hole Number:
XYC-233

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		« 678.40- 681.10 Light grey limestone. »									
		« 681.10- 682.30 Black siliceous mudstone, barren. »									
		« 682.30- 687.10 Medium grey calcareous mudstone with low grade. »									
		« 687.10- 690.10 Light grey limestone »									
		« 690.10- 694.00 Black limestone, barren. »									
		« 694.00- 695.20 Light grey limestone. »									
695.20	719.00	CCMS	630438	695.20	696.20	1.00					
		CCMS – Calcareous Mudstone									
		Massive, calcareous, carbonaceous, dark grey mudstone. Most of the member is massive, but rare poorly defined bedding and pyrite-calcite micro-concretions are present. Most diagnostic structures are feathery calcite beds (=thin calcite-cemented concretions, many of them contain pyrite cores) and calcite pseudo-beds (= fibrous calcite vein parallel to bedding).									
		« lm ca 5.00-10.00mm », « nodules py -3.00% 2.00-20.00mm »,									
		Black siliceous mudstone with calcareous sections, very broken.									
		« 695.20- 697.50 Fault (30% recovery)-whole core is black siliceous mudstone. » « bx 70%» « brco 30%»									
719.00	719.00	EOH									

Diamond Drill Log

Comprehensive Report for Hole:

XYC-232

Hole No.: XYC-232	Depth: 179.00 m	Horizontal Length: 0.00 m	Project: 1710
Location Data:			
Property:	Selwyn Project	Claim Name:	X 14
Mining District:	Selwyn Basin	Grant Number:	Y 64539
Province/Territory:	Yukon		
UTM Co-Ordinates & Altitude of Drill Hole Collar:			
UTM Easting:	489009.45 m	True Azimuth:	210.0 °
UTM Northing:	6926167.20 m	Hole Angle:	-80.0 °
Elevation (m):	1603.80 m	NTS Name:	Placer Creek
		UTM Datum:	NAD 83
		UTM Grid Zone:	9
		NTS Number:	105L06
Grid Co-Ordinates of Drill Hole Collar:			
Grid Easting (m):	0.00 m	Grid Name:	HP 06
Grid Northing (m):	0.00 m	Grid Type:	100m
Grid Azimuth:	270.0 °		
Dimond Drilling Contract:			
Drilled By:	CY-01	Date Drilling Start:	10/16/2010
		Date Finish:	10/19/2010
Diamond Drill Core:			
Logged By:	Kate Cameron / Jelle De	Date Logging Start:	11/06/2010
		Date Finish:	11/13/2010
Legend for Core Logging Codes: PAX			
Core Size:	NQ	Cemented:	Yes
Casing Depth:	7.50 m	Casing Pulled:	Yes
Water Depth:	0.00 m	Overburden Depth:	7.50 m
Level:	Section:	Drift:	

Selwyn Project

Diamond Drill Log

Survey Data for Hole

XYC-232

Hole Comments:

Sat, Oct 16 --- XYC-228 was shut down this morning in CCMS at 231.2m. ACTM-CCMS contact at 207m. The are moving to target number 54 right now, which will become XYC-232.

=====

Sun, Oct 17 --- XYC-232 is actually on target #56, not #54, as was thought. They collared into USMS and hit ACTM at 45 meters. They are now at 47 meters.

=====

Mon, Oct 18 ---"Cyr-01 had issues last night when the helper got his finger caught between the chuck and a pipewrench, he was brought down to camp immediately with a large laceration and broken finger. Then the nightshift fifth man went on as helper, the rods went down without a stabilizer and were pulled again, no core drilled. From dayshift, they are still at 84m. Intersected ACTM at 82m, see what today brings before we know if it is active member or a small mineralized zone. Faulted zone starting at 77m, rods were stuck twice yesterday and once last night in this zone."

=====

Tue, Oct 19 --- Currently in what appears to be CCMS at 147m. They have had two intersections of ACTM, one was hit 81.5m to 97m, low grade, then faulted back into USMS and last night hit ACTM at 125-146m, with some high grade 10-15% zinc zones. They are going to continue drilling to confirm footwall rock.

Wed, Oct 20 ---XYC-232 was shut down yesterday at 179m in CCMS. Moved to setup # 54. XYC-234 total depth 23m. Only up to 20m was emptied into the box this morning, that was 15cm of black broken core, not identifiable. No day shift driller this morning due to shift change

<i>Depth</i>	<i>Dip</i>	<i>Azimuth</i>
0.00	-80.0	210.0
50.00	-79.3	208.7
101.00	-78.1	206.3
152.00	-77.6	202.7
179.00	-76.9	203.6

Selwyn Project Diamond Drill Log

Hole Number:
XYC-232

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
0.00	7.50	OVBR									
7.50	11.60	FLMD <i>FLMD – Flaggy Mudstone Formation</i> <i>Dark grey mudstone in the upper portions of the unit grading into light grey mudstone to siltstone. Contains abundant wispy bioturbation which ranges from randomly-oriented at the top of the unit to bedding-parallel throughout the majority of the unit. Darker upper section has a strong fetid odour along broken surfaces. « btrb 0.10-2.00cm », « cg xtl crns ca 1.00-5.00% 5.00-150.00cm », « crns py 1.00-5.00% 0.10-0.50mm »</i>									
11.60	80.80	USMS <i>USMS – Upper Siliceous Mudstone</i> <i>Consists of interlaminated dark grey to black mudstone and light to medium grey chert. Regionally, a 1m thick graptolite zone occurs 15m below the top of the upper unit, this is usable as a horizon. The USMS is divided into 3 units. The Lower Unit contains abundant limestone concretions and Galena and sphalerite micro-concretions occur locally near the base of this unit. « gra , lm chrt -20.00% », « cg xtl sph crns ca 5.00-20.00cm », « bed chrt 10.00-15.00% »</i> <i>« 11.60- 80.80 Carbonaceous. Less chert banding than usual. »</i> <i>« 11.60- 13.70 Core lost. Flt »« Flt gg 30%»« Flt bx 40%»« Brco 30%»</i> <i>« 26.10- 27.00 Flt »« Flt gg 30%»« Flt bx 70%»</i> <i>« 45.00- 47.60 Mineralized zone. Light grey, laminated. Sphalerite and galena 15-20%. Calcareous mudstone. Abundant calcite veins. »</i> <i>« 59.80- 60.50 Flt »« Flt gg 40%»« Flt bx 60%»</i>	633951	43.70	45.00	1.30	0.06	0.32	1.00	10.00	0.19
			633952	45.00	47.60	2.60	1.17	7.77	6.00	240.00	0.15
			633953	47.60	48.00	0.40	0.02	0.16	1.00	5.00	0.13
			633954	78.70	80.00	1.30	0.01	0.08	1.00	5.00	0.13
			633955	80.00	80.80	0.80	0.18	0.33	1.00	20.00	0.55

Selwyn Project Diamond Drill Log

Hole Number:
XYC-232

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
< @ 63.80 S0 tca 45-60° >											
« 74.00- 80.80 Flt »« Flt gg 5%»« Flt bx 35%»« Brco 20%»											
80.80	98.30	ACTM	633956	80.80	82.20	1.40	1.16	8.46	4.00	290.00	0.14
ACTM – Active Member			633957	82.20	82.50	0.30	2.19	12.18	1.00	570.00	0.18
The ACTM consists of a repetitive, possibly rhythmic, sequence of intercalated carbonaceous mudstone, cherty mudstone, chert and limestone and locally contains economically significant Zn and Pb sulphides (see bold marked facies), mainly in its sections with well developed lamination. Because of its heterogeneity, the member is distinctive and easily identified. ===== The ACTM has 8 different facies: ===== - GREY CHERT FACIES: Consists of laminated medium light grey to medium dark grey chert. Mineralization: 95-99% quartz and up to 5% secondary calcite. - WHITISH GREY ZN-PB MUDSTONE FACIES: Is a laminated cherty rock containing up to 70% sulphides. Mineralization: quartz, sphalerite and galena are the major minerals with only minor amounts of pyrite and locally calcite. Sedimentary diagenetic structures are common and well displayed in the facies, such as: lamination, pseudo-beds, calcite nodules & limestone nodules and abundant water escape structures. Most obvious structure in facies is cross-cutting veins containing massive sphalerite and galena with minor pyrite. They range in width from 0.5 to 10mm. - THIN BEDDED CHERTY MUDSTONE FACIES: Consists of rhythmic intercalated laminae of chert, carbonaceous mudstone and minor micrite. This facies contains significant amounts of Zn and Pb sulphides. - CHERTY MUDSTONE FACIES: Consists of a greyish black monotonous siliceous, carbonaceous mudstone. It is most typically found overlying the thin bedded			633958	82.50	83.20	0.70	2.39	8.05	23.00	260.00	0.30
			633959	83.20	83.60	0.40	0.30	0.99	1.00	20.00	0.30
			633960	83.60	84.50	0.90	1.38	7.83	7.00	200.00	0.18
			633961	83.60	84.50	0.90	1.43	6.24	47.00	170.00	0.23
			633962	84.50	85.30	0.80	0.08	0.44	1.00	5.00	0.18
			633963	85.30	85.80	0.50	0.05	0.62	1.00	5.00	0.08
			633964	85.80	86.80	1.00	5.27	12.20	4.00	420.00	0.43
			633965	86.80	87.20	0.40	1.27	3.41	1.00	110.00	0.37
			633966	87.20	87.30	0.10	0.74	4.52	1.00	110.00	0.16
			633967	87.30	89.00	1.70	1.01	4.41	1.00	130.00	0.23
			633968	89.00	90.30	1.30	0.05	0.02	1.00	5.00	2.50
			633969	90.30	91.60	1.30	0.06	0.27	1.00	5.00	0.22
			633970	91.60	91.60	0.00	0.01	0.01	1.00	5.00	2.00
			633971	91.60	92.90	1.30	0.14	0.43	1.00	5.00	0.33
			633972	92.90	93.30	0.40	0.36	1.33	1.00	20.00	0.27
			633973	93.30	93.70	0.40	0.01	0.01	1.00	5.00	1.00
			633974	93.70	94.70	1.00	0.21	1.90	1.00	40.00	0.11
			633975	94.70	96.40	1.70	0.19	1.48	1.00	40.00	0.13
			633976	96.40	97.10	0.70	0.26	0.28	1.00	5.00	0.93
			633977	97.10	98.30	1.20	0.01	0.03	1.00	5.00	0.33

Selwyn Project Diamond Drill Log

Hole Number:
XYC-232

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		calcareous mudstone facies. - <i>THIN BEDDED CALCAREOUS MUDSTONE FACIES: Consists of laminated carbonaceous mudstone containing 20-40% calcite, 40-55% quartz and 10-20% muscovite. Sulphides occur in laminae. In the XY area it is usually the lowest facies in the section to contain laminated sulphides.</i> - <i>CALCAREOUS MUDSTONE FACIES: Consists of grey to greyish black monotonous, calcareous siliceous carbonaceous mudstone. There are no feathery calcite beds or pyrite-calcite blebs in the facies, making it easily distinguishable from the CCMS.</i> - <i>GRADED LIMESTONE FACIES: Is a laminated argillaceous limestone with intercalated carbonaceous limestone laminae. The main rock type in the facies is laminated limestone with laminae up to 0.1-7mm thick.</i> - <i>LIGHT GREY BASAL LIMESTONE FACIES - LGLS: Consists of laminated argillaceous limestone. In the Anniv area it marks the end of the ACTM. It's not always present in the stratigraphy.</i> - <i>BASAL FACIES: This is a highly contorted and locally foliated carbonaceous mudstone. Unlike the other facies it is not repeated higher in the member. It appears locally to contain the slip zone of a major slump. The facies has only been observed in the YX area. It is 0.1-2m thick. The facies consists of massive carbonaceous siliceous mudstone with lenses and laminae of contorted, slightly carbonaceous chert.</i> « 80.80- 92.20 High grade. Black silicious mudstone with sphalerite and galena laminae. Niton reading is distorted by high Pb content (Pb: 60%, Zn: 30%). Visual estimate: Pb 15%; Zn 20% » « 82.20- 82.50 Light grey silicious mudstone with abundant galena and sphalerite in laminae. »									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-232

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		« 82.50- 83.20 Excellent mineralization. Black mudstone with abundant sphalerite and galena laminae. »									
		« 83.20- 83.60 Light grey limestone. »									
		« 83.60- 84.50 Black silicious mudstone with some mineralization, mostly as sphalerite in laminae. Whole section is broken up and turned in the drill. »									
		« 84.50- 85.30 Light to medium grey limestone. Internally laminated, not a concretion. »									
		« 85.30- 85.80 Medium grey, weakly laminated silicious mudstone. No visible mineralization. »									
		« 85.80- 86.80 Medium to slightly darker grey limestone and calcareous mudstone. Laminated. Mineralized. Sphalerite and some galena in laminae. »									
		« 86.80- 87.30 Light grey laminated mudstone. Some mineralization. »									
		« 87.20- 87.30 Black mudstone, laminated. No visible mineralization. »									
		« 87.30- 89.00 Light (sometimes towards medium) grey limestone. Internal laminae are conformable to over and underlying mudstone- therefor, formed by some deposition process with different material. No visible mineralization. »									
		« 89.00- 90.30 Medium grey calcareous mudstone with clasts or concretions of limestone <10cm wide. Some minor sphalerite is possible in mudstone laminae, but weak. »									
		« 90.30- 91.60 Dark grey to black silicious mudstone with calcite veins parallel to weak laminae. Faulted. Minor mineralization. »									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-232

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
« 90.30- 90.60 Flt »« Flt gg 20%»« Flt bx 80%»											
« 91.40- 91.60 Flt »« Flt gg 20%»« Flt bx 60%»											
« 91.60- 92.90 Medium grey limestone with internal laminae conformable to surrounding mudstone. No visible mineralization. »											
« 92.90- 93.30 Dark grey calcareous mudstone, laminated. No visible mineralization. »											
« 93.30- 93.70 Light grey limestone with conformable laminae. No visible mineralization. »											
« 93.70- 94.70 Dark grey to black mudstone, laminated. Minor sphalerite mineralization visible. Calcareous. »											
« 94.70- 96.40 Silicious black mudstone with CCMS-like veining. No visible mineralization. »											
« 95.20- 95.30 Flt »« Flt gg 30%»« Flt bx 70%»											
« 96.40- 97.10 Black mudstone with limestone banding and multitude of wispy calcite stringers. No visible mineralization. »											
« 97.10- 98.30 Light grey limestone. Basal limestone. Laminae are conformable to mudstone above and wispy calcite veins below. »											
98.30	110.60	CCMS	633978	98.30	99.80	1.50	0.01	0.03	1.00	5.00	0.33
CCMS – Calcareous Mudstone			633979	99.80	101.00	1.20	0.02	0.23	1.00	5.00	0.09
			633980	101.00	101.00	0.00	1.42	2.91	19.00	180.00	0.49
Massive, calcareous, carbonaceous, dark grey mudstone. Most of the member is massive, but rare poorly defined bedding and pyrite-calcite micro-concretions are present. Most diagnostic structures are feathery calcite beds (=thin calcite-cemented concretions, many of them contain pyrite cores) and calcite											

Selwyn Project Diamond Drill Log

Hole Number:
XYC-232

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		pseudo-beds (= fibrous calcite vein parallel to bedding). « lm ca 5.00-10.00mm », « nodules py -3.00% 2.00-20.00mm » ◁ @ 102.60 S0 in planar parallel calcite veins. S0 tca 35° ▷									
110.60	112.00	FLT									
		« 110.60- 112.00 First 60cm is solid calcite with minor quartz. After that there is about 40cm of reconsolidated breccia consisting of limestone clasts and calcite veining. Poor recovery, as 40cm is missing. Flt »									
112.00	125.00	USMS	633981	123.70	124.40	0.70	0.01	0.09	1.00	5.00	0.11
		USMS – Upper Siliceous Mudstone	633982	124.40	125.00	0.60	0.01	0.09	1.00	5.00	0.11
		Consists of interlaminated dark grey to black mudstone and light to medium grey chert. Regionally, a 1m thick graptolite zone occurs 15m below the top of the upper unit, this is usable as a horizon. The USMS is divided into 3 units. The Lower Unit contains abundant limestone concretions and Galena and sphalerite micro-concretions occur locally near the base of this unit. « gra , lm chrt -20.00% », « cg xtl sph crns ca 5.00-20.00cm », « bed chrt 10.00-15.00% » ◁ @ 113.80 S0 defined by chert bands. S0 tca 64° ▷ ◁ @ 115.40 S0 defined by chert bands. S0 tca 67° ▷ ◁ @ 118.10 S0 defined by chert bands. S0 tca 72° ▷ « 123.70- 125.00 Flt »« Flt gg 30%»« Flt bx 30%»« Brco 15%»									
125.00	146.20	ACTM	633983	125.00	125.20	0.20	1.49	9.02	4.00	280.00	0.17
		ACTM – Active Member	633984	125.20	125.70	0.50	0.12	0.81	1.00	20.00	0.15
			633985	125.70	126.60	0.90	1.92	9.35	3.00	240.00	0.21
			633986	126.60	126.90	0.30	5.62	0.89	2.00	30.00	6.31
			633987	126.90	128.00	1.10	0.30	1.99	1.00	70.00	0.15
			633988	128.00	128.70	0.70	0.03	0.05	1.00	5.00	0.60
			633989	128.70	129.20	0.50	1.53	10.75	3.00	280.00	0.14
			633990	129.20	130.90	1.70	0.44	0.57	1.00	20.00	0.77
			633991	129.20	130.90	1.70	0.48	1.39	1.00	40.00	0.35

Selwyn Project Diamond Drill Log

Hole Number:
XYC-232

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
=====			633992	130.90	131.40	0.50	0.92	4.41	1.00	110.00	0.21
		The ACTM has 8 different facies:	633993	131.40	132.40	1.00	0.71	3.27	1.00	90.00	0.22
=====			633994	132.40	132.80	0.40	2.26	14.87	4.00	350.00	0.15
		- GREY CHERT FACIES: Consists of laminated medium light grey to medium dark grey chert. Mineralization: 95-99% quartz and up to 5% secondary calcite.	633995	132.80	133.60	0.80	2.11	5.78	1.00	140.00	0.37
		- WHITISH GREY ZN-PB MUDSTONE FACIES: Is a laminated cherty rock containing up to 70% sulphides. Mineralization: quartz, sphalerite and galena are the major minerals with only minor amounts of pyrite and locally calcite. Sedimentary diagenetic structures are common and well displayed in the facies, such as: lamination, pseudo-beds, calcite nodules & limestone nodules and abundant water escape structures. Most obvious structure in facies is cross-cutting veins containing massive sphalerite and galena with minor pyrite. They range in width from 0.5 to 10mm.	633996	133.60	134.30	0.70	0.47	2.49	1.00	60.00	0.19
			633997	134.30	135.20	0.90	0.68	5.63	1.00	150.00	0.12
			633998	135.20	136.10	0.90	0.29	1.20	1.00	30.00	0.24
			633999	136.10	137.00	0.90	2.34	0.46	1.00	10.00	5.09
			634000	137.00	137.00	0.00	0.01	0.01	1.00	5.00	2.00
			634651	137.00	138.20	1.20	0.03	0.03	1.00	5.00	1.00
			634652	138.20	139.00	0.80	0.08	0.47	1.00	10.00	0.17
			634653	139.00	140.20	1.20	0.52	1.25	2.00	30.00	0.42
			634654	140.20	140.70	0.50	0.43	0.36	2.00	10.00	1.19
			634655	140.70	141.70	1.00	0.13	1.20	1.00	30.00	0.11
			634656	141.70	142.60	0.90	0.28	1.88	3.00	40.00	0.15
			634657	142.60	143.50	0.90	0.29	1.55	3.00	40.00	0.19
			634658	143.50	144.40	0.90	0.08	0.86	2.00	30.00	0.09
			634659	144.40	144.60	0.20	0.07	0.12	1.00	5.00	0.58
			634660	144.60	144.60	0.00	5.93	6.97	70.00	190.00	0.85
			634661	144.60	145.00	0.40	0.19	0.32	2.00	5.00	0.59
			634662	145.00	146.20	1.20	0.05	0.01	1.00	5.00	10.00
		- CHERTY MUDSTONE FACIES: Consists of a greyish black monotonous siliceous, carbonaceous mudstone. It is most typically found overlying the thin bedded calcareous mudstone facies.									
		- THIN BEDDED CALCAREOUS MUDSTONE FACIES: Consists of laminated carbonaceous mudstone containing 20-40% calcite, 40-55% quartz and 10-20% muscovite. Sulphides occur in laminae. In the XY area it is usually the lowest facies in the section to contain laminated sulphides.									
		- CALCAREOUS MUDSTONE FACIES: Consists of grey to greyish black monotonous, calcareous siliceous carbonaceous mudstone. There are no feathery calcite beds or pyrite-calcite blebs in the facies, making it easily distinguishable from the CCMS.									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-232

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		- <i>GRADED LIMESTONE FACIES: Is a laminated argillaceous limestone with intercalated carbonaceous limestone laminae. The main rock type in the facies is laminated limestone with laminae up to 0.1-7mm thick.</i> - <i>LIGHT GREY BASAL LIMESTONE FACIES - LGLS: Consists of laminated argillaceous limestone. In the Anniv area it marks the end of the ACTM. It's not always present in the stratigraphy.</i> - <i>BASAL FACIES: This is a highly contorted and locally foliated carbonaceous mudstone. Unlike the other facies it is not repeated higher in the member. It appears locally to contain the slip zone of a major slump. The facies has only been observed in the YX area. It is 0.1-2m thick. The facies consists of massive carbonaceous siliceous mudstone with lenses and laminae of contorted, slightly carbonaceous chert.</i> « 125.00- 125.20 Mainly silicious mudstone with moderately developed lamination. Fairly rich in pyrite. Mineralization: 9.5% Zn, 3.5% Pb, 9% Fe » « 125.20- 125.70 Carbonate concretion. Mineralization <1% Zn+Pb » « 125.70- 126.60 Silicious mudstone with minor intercalated limestone clasts. Mudstone has a moderately to well developed lamination. Mineralization: 6% Zn, 2% Pb. » « 126.60- 126.90 Carbonate concretion with galena blebs. Mineralization: 0.7% Zn, 1.4% Pb » « 126.90- 128.70 Poorly mineralized slightly calcareous mudstone with no lamination. <1% Zn+Pb » « 128.70- 129.20 Mainly silicious mudstone with well developed lamination and minor intercalated limestone. Mineralization: 9% Zn, 3% Pb. »									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-232

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
« 129.20- 130.90 Mainly limestone. Poorly mineralized: <1.5% Zn +Pb »											
« 130.90- 132.40 Calcareous mudstone with moderately developed lamination and limestone. 2% Zn, 0.5% Pb. »											
« 132.40- 132.80 5cm of high grade ore and mineralized carbonate concretion with moderately developed lamination. 6% Zn, 1% Pb »											
« 132.80- 137.00 Mainly limestone with minor visible galena blebs and calcareous mudstone with no to poorly developed lamination, except for a 15cm long section. »											
« 137.00- 138.20 Thinly bedded limestone. »											
« 138.20- 140.20 Calcareous carbonaceous mudstone with 1.5% Zn and 0.5% Pb. »											
« 140.20- 140.70 Very calcareous mudstone, rich in calcite. Minor limestone. Barren. »											
« 140.70- 144.40 Poorly mineralized calcareous mudstone with no lamination. Less than 2% Zn +Pb »											
« 144.40- 144.60 Calcareous mudstone rich in calcite and some unknown mineral (0.2% Ni and 1.2% V) resembling a mica. »											
« 144.60- 145.00 Poorly mineralized calcareous mudstone. <1% Zn+Pb »											
« 145.00- 146.20 Basal light grey limestone. »											
146.20	179.00	CCMS	634663	146.20	146.80	0.60	0.05	0.06	2.00	5.00	0.83
CCMS – Calcareous Mudstone			634664	146.80	147.70	0.90	0.06	0.80	3.00	40.00	0.08
Massive, calcareous, carbonaceous, dark grey mudstone. Most of the member is massive, but rare poorly defined bedding and pyrite-calcite micro-concretions are present. Most diagnostic structures are feathery calcite beds (=thin											

Selwyn Project Diamond Drill Log

Hole Number:
XYC-232

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		calcite-cemented concretions, many of them contain pyrite cores) and calcite pseudo-beds (= fibrous calcite vein parallel to bedding). « lm ca 5.00-10.00mm », « nodules py -3.00% 2.00-20.00mm » < @ 156.20 S0 defined by faint beds consisting of disseminated pyrite. S0 tca 78° > < @ 159.40 S0 defined by faint beds consisting of disseminated pyrite. S0 tca 70° > < @ 162.50 S0 defined by faint beds consisting of disseminated pyrite. S0 tca 60° > < @ 169.70 S0 defined by faint beds consisting of disseminated pyrite. S0 tca 74° > < @ 170.80 S0 defined by faint beds consisting of disseminated pyrite. S0 tca 73° > « 172.80- 176.50 Flt »« Flt gg 30%»« Flt bx 30%»« Brco 30%» < @ 177.20 S0 defined by a 2mm thick chert band. S0 tca 61° > « 176.50- 179.00 Section of rock similar to the above described USMS from 112.0m to 125.0m. Could be USMS again or this and the other section may be an atypical range feature in "CCMS". In that case, the repeat in "ACTM" was caused by the 1.3m fault just above it. »									
179.00	179.00	EOH									

Diamond Drill Log

Comprehensive Report for Hole:

XYC-231

Hole No.: XYC-231	Depth: 259.50 m	Horizontal Length: 0.00 m	Project: 1710
Location Data:			
Property:	Selwyn Project	Claim Name:	X 13
Mining District:	Selwyn Basin	Grant Number:	Y 64538
Province/Territory:	Yukon		
UTM Co-Ordinates & Altitude of Drill Hole Collar:			
UTM Easting:	488663.02 m	True Azimuth:	204.0 °
UTM Northing:	6926458.96 m	Hole Angle:	-75.0 °
Elevation (m):	1625.70 m	NTS Name:	Placer Creek
		UTM Datum:	NAD 83
		UTM Grid Zone:	9
		NTS Number:	105L06
Grid Co-Ordinates of Drill Hole Collar:			
Grid Easting (m):	0.00 m	Grid Name:	HP 06
Grid Northing (m):	0.00 m	Grid Type:	100m
Grid Azimuth:	264.0 °		
Dimond Drilling Contract:			
Drilled By:	NL-01	Date Drilling Start:	10/16/2010
		Date Finish:	10/20/2010
Diamond Drill Core:			
Logged By:	Kate Cameron / Graham	Date Logging Start:	10/31/2010
		Date Finish:	10/29/2010
Legend for Core Logging Codes: PAX			
Core Size:	NQ/NQ3	Cemented:	Yes
Casing Depth:	6.70 m	Casing Pulled:	Yes
Water Depth:	0.00 m	Overburden Depth:	6.70 m
Level:			
Section:			
Drift:			

Selwyn Project

Diamond Drill Log

Survey Data for Hole

XYC-231

Hole Comments:

Sat, Oct 16 --- The core barrel and tube were stuck in the hole yesterday, possibly due to poor circulation of water and mud around the bit. After extensive efforts aimed at retrieving the barrel and/or tube failed, it was decided to abandon the hole and drill XYC-231 on target 14a, 1 meter to the north, at the same azimuth and dip. The are now pulling rods from the abandoned hole, and will shift over to the new hole and begin drilling today.

=====

Sun, Oct 17 --- Yesterday we successfully shifted the drill back approximately 1 meter and began again on target 14a, XYC-231. 20 feet of casing was put down, with no problems to report. No night shift. This hole is being drilled at the originally intended inclination of -75 degrees.

=====

Mon, Oct 18 ---Yesterday dayshift drilled 20 meters through apparently fractured, blocky ground with poor circulation. However, the driller believes that the problems experienced on the last setup (XYC-227 - same pad) can be avoided. We did not see the core, as this crew had a truck problem and the core was left in the back of their truck near XY. No nightshift.

=====

Tue, Oct 19 --- Collared into and currently drilling through FLMD at 59 meters. A small problem with the chuck will require replacement, but they can continue to drill for now.

=====

Wed, Oct 20 ---Drilling through FLMD at 107 meters. Core is competent and the drilling has been good. The driller, now understanding what the ground is like, has been able to anticipate and prevent the problems experienced on XYC-227, so far.

=====

Thu, Oct 21 --- Drilling at 131 meters through competent USMS. No problems and no nightshift.

=====

Fri, Oct 22 --- Slow drilling through broken USMS at 148 meters. No serious problems.

=====

Sat, Oct 23 --- Slow drilling in competent USMS at 162 meters.

=====

Sun, Oct 24 --- Difficult drilling; USMS at 171 meters after drilling only 9 meters yesterday. The last box is still at the drill (not full), but apparantly there was very poor recovery for much of the day yesterday. No return in the hole. Core that has been brought back to camp is quite competent.

=====

Mon, Oct 25 ---Poor recovery and slow drilling in USMS at 194 meters. Faulted / broken-up throughout the past 23 meters; wire line broke and was fixed yesterday, still no return. No nightshift.

=====

Tue, Oct 26 --- Slow drilling at 206 meters. The core is was unexpected: Typical, competent USMS to 197 meters, where we hit a 3 meter bed of very light grey, somewhat sheared-looking limestone, identical to the typical basal limestone facies of Active Member. At approximately 200 meters the limestone changes to dark grey mudstone, broken up but resembling CCMS. Will have to drill more, but we may have a dry hole here. No sign of mineralization.

=====

Selwyn Project

Diamond Drill Log

Survey Data for Hole

XYC-231

Wed, Oct 27 ---Slow drilling at 225 meters in mudstone that resembles CCMS. I believe we have a dry hole, after seeing the apparant end of USMS and passing through what strongly resembled typical basal limestone. I do believe that we should drill to the target depth, however, in case we simply have a misleading stretch of USMS on our hands. Will continue drilling.

=====

Thu, Oct 28 --- At 243 meters in CCMS. Greg will look at the core this afternoon, and if we are past the target depth and there is no change he will shut it down and prepare to begin a move to Don Deposit tomorrow.

=====

Fri, Oct 29 --- Shut down yesterday at 259.5m in CCMS. Will cement above the faux-ACTM and prepare for the long move to d36 in the Don Zone, which should commence this afternoon.

<i>Depth</i>	<i>Dip</i>	<i>Azimuth</i>
0.00	-75.0	204.0
50.00	-73.6	205.4
101.00	-72.4	208.3
150.00	-72.0	210.5
201.00	-70.6	210.4
250.00	-70.1	212.5

Selwyn Project Diamond Drill Log

Hole Number:
XYC-231

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
0.00	6.70	OVBR									
6.70	92.60	FLMD									
FLMD – Flaggy Mudstone Formation											
Dark grey mudstone in the upper portions of the unit grading into light grey mudstone to siltstone. Contains abundant wispy bioturbation which ranges from randomly-oriented at the top of the unit to bedding-parallel throughout the majority of the unit. Darker upper section has a strong fetid odour along broken surfaces. « btrb 0.10-2.00cm », « cg xtl crns ca 1.00-5.00% 5.00-150.00cm », « crns py 1.00-5.00% 0.10-0.50mm »											
« 6.70- 92.60 Typical FLMD. Medium to light grey, competent. »											
« 6.70- 31.70 Near surface broken ground. Flt »« Flt gg 2%»« Flt bx 20%»« Brco 10%»											
‹ @ 33.10 S0 defined by darker band, 1cm wide, parallel to bioturbations. S0 tca 65° ‹											
« 80.00- 80.90 Quartz vein (several smaller ones within 10m below as well). »											
92.60	196.80	USMS	635251	180.50	181.20	0.70	0.50	0.99	1.00	30.00	0.51
USMS – Upper Siliceous Mudstone			635252	181.20	182.00	0.80	0.45	6.96	1.00	160.00	0.06
			635253	182.00	182.60	0.60	0.06	0.12	1.00	5.00	0.50
Consists of interlaminated dark grey to black mudstone and light to medium grey chert. Regionally, a 1m thick graptolite zone occurs 15m below the top of the upper unit, this is usable as a horizon. The USMS is divided into 3 units. The Lower Unit contains abundant limestone concretions and Galena and sphalerite micro-concretions occur locally near the base of this unit. « gra , lm chrt -20.00% », « cg xtl sph crns ca 5.00-20.00cm », « bed chrt 10.00-15.00% »			635254	182.60	187.00	4.40	0.07	0.15	1.00	5.00	0.47
			635255	187.00	189.10	2.10	0.01	0.02	2.00	5.00	0.50
			635256	189.10	190.70	1.60	0.01	0.48	1.00	30.00	0.02
			635257	190.70	191.70	1.00	0.06	0.77	9.00	50.00	0.08
			635258	191.70	194.10	2.40	0.01	0.48	3.00	30.00	0.02
			635259	194.10	195.70	1.60	0.12	0.37	4.00	10.00	0.32
			635260	195.70	196.80	1.10	0.06	0.61	2.00	20.00	0.10
« 112.00- 112.10 No loss of length. Flt »« Flt gg 100%»			635261	195.70	196.80	1.10	0.11	0.57	4.00	20.00	0.19

Selwyn Project Diamond Drill Log

Hole Number:
XYC-231

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		« 126.80- 126.90 No loss. Flt »« Flt gg 50%»« Flt bx 50%»									
		« 131.00- 138.00 Calcite veins increase. Pyrite blebs more frequent. »									
		« 138.00- 165.00 Typical USMS with noteworthy features: Recrystallized qt-cal veins truncated by carbonaceous mudstone creating a serated saw-tooth pattern to the veins. Laminated, rounded limestone clasts deforming S0 (3-15cm). Limestone, laminated layers up to 50cm thick commonly scour out mudstone at base. Framboidal pyrite 2-8mm diameter, sometimes squiggly and elongated. S0 is highly variable. Limestone layers are normally graded. Pyrite veinlets are commonly broken up. Some veins have coarse grained recrystallized qt- infilling voids.»									
		« 165.00- 170.40 Fracture zone, reconstituted medium grey mudstone. Abundant thin (<2mm) calcite and qt veinlets infill fractures. »									
		« 170.40- 189.00 Blocky ground, discontinuously fractured and faulted, pseudotachylite development is moderate. Patchy zones of weak Pb Zn mineralization <1% combined in sections no greater than 5-10cm »									
		« 190.70- 191.70 Zones of ~100% drill filings with some rare breccia fragments. »									
		« 191.70- 194.90 Many plane-failure pieces 1-10cm thick. Flt »« Flt gg 5%»« Flt bx 10%»« Brco 85%»									
		« 194.90- 196.80 Typical dark-grey-black USMS as described. »									
		« 165.00- 196.80 At the base of the USMS unit there has been extensive faulting that may have emoved the mineralized section of the active member, and only left ~4m of basal limestone behind to indicate there once was actm here. Throughout this lower interval of usms the only base metal mineralization is seen, the basal limestone is essentially barren. Combined Pb/Zn can reach up to 0.5% combined in the usms, however; it is patchy and weakly disseminated as very fine grained crystals. »									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-231

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
196.80	210.90	ACTM									
<i>ACTM – Active Member</i>			635262	196.80	198.30	1.50	0.01	0.01	1.00	5.00	2.00
<i>The ACTM consists of a repetitive, possibly rhythmic, sequence of intercalated carbonaceous mudstone, cherty mudstone, chert and limestone and locally contains economically significant Zn and Pb sulphides (see bold marked facies), mainly in its sections with well developed lamination. Because of its heterogeneity, the member is distinctive and easily identified.</i> ===== <i>The ACTM has 8 different facies:</i> ===== - GREY CHERT FACIES: Consists of laminated medium light grey to medium dark grey chert. Mineralization: 95-99% quartz and up to 5% secondary calcite. - WHITISH GREY ZN-PB MUDSTONE FACIES: Is a laminated cherty rock containing up to 70% sulphides. Mineralization: quartz, sphalerite and galena are the major minerals with only minor amounts of pyrite and locally calcite. Sedimentary diagenetic structures are common and well displayed in the facies, such as: lamination, pseudo-beds, calcite nodules & limestone nodules and abundant water escape structures. Most obvious structure in facies is cross-cutting veins containing massive sphalerite and galena with minor pyrite. They range in width from 0.5 to 10mm. - THIN BEDDED CHERTY MUDSTONE FACIES: Consists of rhythmic intercalated laminae of chert, carbonaceous mudstone and minor micrite. This facies contains significant amounts of Zn and Pb sulphides. - CHERTY MUDSTONE FACIES: Consists of a greyish black monotonous siliceous, carbonaceous mudstone. It is most typically found overlying the thin bedded calcareous mudstone facies.			635263	198.30	200.00	1.70	0.01	0.01	1.00	5.00	2.00
			635264	200.00	200.90	0.90	0.01	0.01	1.00	5.00	2.00
			635265	200.90	202.50	1.60	0.01	0.01	1.00	5.00	1.00
			635266	202.50	204.20	1.70	0.01	0.68	2.00	30.00	0.01
			635267	204.20	205.30	1.10	0.01	0.13	1.00	5.00	0.08
			635268	205.30	206.40	1.10	0.17	0.29	1.00	5.00	0.59
			635269	206.40	208.90	2.50	0.21	0.93	2.00	30.00	0.23
			635270	208.90	208.90	0.00	0.01	0.01	1.00	5.00	2.00
			635271	208.90	209.20	0.30	0.35	1.28	4.00	40.00	0.27
			635272	209.20	210.00	0.80	0.14	0.91	4.00	30.00	0.15
			635273	210.00	210.90	0.90	0.35	0.92	5.00	30.00	0.38

Selwyn Project Diamond Drill Log

Hole Number:
XYC-231

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		- <i>THIN BEDDED CALCAREOUS MUDSTONE FACIES: Consists of laminated carbonaceous mudstone containing 20-40% calcite, 40-55% quartz and 10-20% muscovite. Sulphides occur in laminae. In the XY area it is usually the lowest facies in the section to contain laminated sulphides.</i> - <i>CALCAREOUS MUDSTONE FACIES: Consists of grey to greyish black monotonous, calcareous siliceous carbonaceous mudstone. There are no feathery calcite beds or pyrite-calcite blebs in the facies, making it easily distinguishable from the CCMS.</i> - <i>GRADED LIMESTONE FACIES: Is a laminated argillaceous limestone with intercalated carbonaceous limestone laminae. The main rock type in the facies is laminated limestone with laminae up to 0.1-7mm thick.</i> - <i>LIGHT GREY BASAL LIMESTONE FACIES - LGLS: Consists of laminated argillaceous limestone. In the Anniv area it marks the end of the ACTM. It's not always present in the stratigraphy.</i> - <i>BASAL FACIES: This is a highly contorted and locally foliated carbonaceous mudstone. Unlike the other facies it is not repeated higher in the member. It appears locally to contain the slip zone of a major slump. The facies has only been observed in the YX area. It is 0.1-2m thick. The facies consists of massive carbonaceous siliceous mudstone with lenses and laminae of contorted, slightly carbonaceous chert.</i> « 196.80- 210.90 Light-grey, laminated, calcite-qt-rich limestone. Minor pyrite associated with some qt-calcite veins, which tend to be conformable. Minor amount of fine grained light grey rounded and elongated limestone clasts. Barren to visible mineralization. » « 200.90- 204.20 Dark grey carbonaceous mudstone with abundant qt and calcite veining. Laminae are distorted from veining intrusion. Minor trace									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-231

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		disseminated pyrite. Broken up easily by drill due to high intensity of fracturing. Fault breccia and gouge zones are common, typically between 2-8cm thick. No visible base metal mineralization. »									
		« 204.20- 209.20 Intercalated laminated limestone, silicious and carbonaceous mudstone- similar to USMS. Light to dark grey limestone and massive pyrite beds 3-7cm thick. High rate of fracturing produces blocky ground, two stage veining also helps to fracture rock up. Mudstone layers are moderately calcareous. »									
		« 209.20- 210.90 Typical light grey basal limestone, finely laminated with randomly oriented calcite and quartz veins 1-8mm thick. No visible base metal mineralization. Mud component increases near base of interval. Appears to be in stratigraphic contact with 'CCMS' »									
210.90	259.50	CCMS	635274	210.90	210.90	0.00	6.23	6.78	72.00	190.00	0.92
		CCMS – Calcareous Mudstone	635275	210.90	212.70	1.80	0.01	0.01	2.00	5.00	2.00
			635276	212.70	212.70	0.00	1.41	2.95	18.00	180.00	0.48
		Massive, calcareous, carbonaceous, dark grey mudstone. Most of the member is massive, but rare poorly defined bedding and pyrite-calcite micro-concretions are present. Most diagnostic structures are feathery calcite beds (=thin calcite-cemented concretions, many of them contain pyrite cores) and calcite pseudo-beds (= fibrous calcite vein parallel to bedding).									
		« lm ca 5.00-10.00mm », « nodules py -3.00% 2.00-20.00mm »									
		« 210.90- 259.50 The interval of CCMS is typical of this unit. Intercalated calcareous mudstone and muddy limestone generally display a fissile and brittle fracture. High carbon content is often associated with increased brittle fracture. The calcareous component tends to strengthen the rock against brittle shear. Pyrite (0.2-2mm crystals) occur with quartz and calcite remobilized fluids and often surround circular agglomerations of framboidal pyrite. Pyrite is the only sulphide mineral observed and occurs in many fashions; disseminated, stringer, specular, pseudo-beds, framboids. The entire interval is moderately fractured in a fissile fashion, with numerous natural fractures. »									

[illegible]

Diamond Drill Log

Comprehensive Report for Hole:

XYC-230

Hole No.: XYC-230	Depth: 176.00 m	Horizontal Length: 0.00 m	Project: 1710
Location Data:			
Property:	Selwyn Project	Claim Name:	X 14
Mining District:	Selwyn Basin	Grant Number:	Y 64539
Province/Territory:	Yukon		
UTM Co-Ordinates & Altitude of Drill Hole Collar:			
UTM Easting:	488768.19 m	True Azimuth:	46.0 °
UTM Northing:	6926226.10 m	Hole Angle:	-85.0 °
Elevation (m):	1583.69 m	NTS Name:	Placer Creek
		NTS Number:	105L06
Grid Co-Ordinates of Drill Hole Collar:			
Grid Easting (m):	0.00 m	Grid Name:	HP 06
Grid Northing (m):	0.00 m	Grid Type:	100m
Grid Azimuth:	106.0 °		
Dimond Drilling Contract:			
Drilled By:	CY-02	Date Drilling Start:	10/16/2010
		Date Finish:	10/20/2010
Diamond Drill Core:			
Logged By:	Kate Cameron / Jelle De	Date Logging Start:	11/06/2010
		Date Finish:	11/15/2010
Legend for Core Logging Codes: PAX			
Core Size:	NQ	Cemented:	Yes
Casing Depth:	9.60 m	Casing Pulled:	Yes
Water Depth:	0.00 m	Overburden Depth:	9.60 m
Level:	Section:	Drift:	

Selwyn Project

Diamond Drill Log

Survey Data for Hole

XYC-230

Hole Comments:

Sat, Oct 16 --- XYC-229 was shut down yesterday evening at 237m in Transition formation. Greg is currently having the drill spun around to drill target #59. This will be XYC-230.

=====

Sun, Oct 17 --- We had issues last night, with the casing shoe somehow catching on the bit as it was being drilled. This caused 10ft of casing and the shoe to advance with the rods to a total depth of about 13m. This hole has to be abandoned and started again. The drill is currently being pulled back one meter to start again on the same azimuth and dip. Because only a few feet of core was drilled, this new hole will still be XYC-230, target #59.

=====

Mon, Oct 18 ---Cyr-02 Went back down with casing yesterday after issues on the first attempt of the casing shoe catching on the bit and dropping the casing down with the rods. They are now at 38m in USMS. Very broken core from 23m on.

=====

Tue, Oct 19 --- Drilling at 140m. We are in the middle of what appears to be a large ACTM intersection from approximately 69.5 to 139.5 meters, with mineralized zones at 69.5m-84m and 124m-139.5m with barren ACTM in between. We may find upon logging that a fault after the first mineralized zone caused a repetition of ACTM, but not at first examination. Will continue drilling.

<i>Depth</i>	<i>Dip</i>	<i>Azimuth</i>
0.00	-85.0	46.0
50.00	-85.8	52.3
101.00	-86.3	56.4
161.00	-86.5	63.7
173.00	-85.5	66.1

Selwyn Project Diamond Drill Log

Hole Number:
XYC-230

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%	
0.00	9.60	OVBR										
9.60	69.50	USMS	635301	66.40	68.00	1.60	0.01	0.26	1.00	5.00	0.04	
USMS – Upper Siliceous Mudstone Consists of interlaminated dark grey to black mudstone and light to medium grey chert. Regionally, a 1m thick graptolite zone occurs 15m below the top of the upper unit, this is usable as a horizon. The USMS is divided into 3 units. The Lower Unit contains abundant limestone concretions and Galena and sphalerite micro-concretions occur locally near the base of this unit. « gra , lm chrt -20.00% », « cg xtl sph crns ca 5.00-20.00cm », « bed chrt 10.00-15.00% » « 9.60- 69.50 Typical USMS with small >1m sections of massive limestone. » « 23.00- 55.40 Multiple faults. Flt »« Flt gg 15%»« Flt bx 45%»« Brco 20%» « 53.90- 55.40 Flt »« Flt gg 10%»« Flt bx 60%»« Brco 30%» « 59.00- 74.90 Some slick-n-sides present. Very fractured zone. Flt »« Flt gg 10%»« Flt bx 20%»« Brco 10%»			635302	68.00	69.50	1.50	0.05	0.34	1.00	5.00	0.15	
69.50	87.90	ACTM	635303	69.50	70.40	0.90	1.65	7.10	3.00	270.00	0.23	
ACTM – Active Member The ACTM consists of a repetitive, possibly rhythmic, sequence of intercalated carbonaceous mudstone, cherty mudstone, chert and limestone and locally contains economically significant Zn and Pb sulphides (see bold marked facies), mainly in its sections with well developed lamination. Because of its heterogeneity, the member is distinctive and easily identified. ===== The ACTM has 8 different facies: =====			635304	70.40	73.50	3.10	0.95	5.15	1.00	240.00	0.18	
			635305	73.50	74.90	1.40	1.03	6.59	1.00	180.00	0.16	
			635306	74.90	76.50	1.60	0.29	0.47	1.00	10.00	0.62	
			635307	76.50	78.10	1.60	0.89	5.39	1.00	130.00	0.17	
			635308	78.10	78.40	0.30	0.59	2.72	1.00	80.00	0.22	
			635309	78.40	79.20	0.80	1.35	4.43	2.00	100.00	0.30	
			635310	79.20	80.20	1.00	9.95	22.06	8.00	900.00	0.45	
			635311	79.20	80.20	1.00	8.10	18.43	6.00	740.00	0.44	
			635312	80.20	81.10	0.90	5.93	12.67	5.00	460.00	0.47	
			635313	81.10	81.50	0.40	0.12	0.15	1.00	5.00	0.80	
			635314	81.50	83.30	1.80	0.71	1.42	1.00	30.00	0.50	
			635315	83.30	83.50	0.20	0.01	0.08	1.00	5.00	0.13	

Selwyn Project Diamond Drill Log

Hole Number:
XYC-230

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		- GREY CHERT FACIES: Consists of laminated medium light grey to medium dark grey chert. Mineralization: 95-99% quartz and up to 5% secondary calcite.	635316	83.50	85.00	1.50	0.21	0.83	1.00	20.00	0.25
			635317	85.00	86.50	1.50	0.16	0.89	1.00	20.00	0.18
		- WHITISH GREY ZN-PB MUDSTONE FACIES: Is a laminated cherty rock containing up to 70% sulphides. Mineralization: quartz, sphalerite and galena are the major minerals with only minor amounts of pyrite and locally calcite. Sedimentary diagenetic structures are common and well displayed in the facies, such as: lamination, pseudo-beds, calcite nodules & limestone nodules and abundant water escape structures. Most obvious structure in facies is cross-cutting veins containing massive sphalerite and galena with minor pyrite. They range in width from 0.5 to 10mm.									
		- THIN BEDDED CHERTY MUDSTONE FACIES: Consists of rhythmic intercalated laminae of chert, carbonaceous mudstone and minor micrite. This facies contains significant amounts of Zn and Pb sulphides.									
		- CHERTY MUDSTONE FACIES: Consists of a greyish black monotonous siliceous, carbonaceous mudstone. It is most typically found overlying the thin bedded calcareous mudstone facies.									
		- THIN BEDDED CALCAREOUS MUDSTONE FACIES: Consists of laminated carbonaceous mudstone containing 20-40% calcite, 40-55% quartz and 10-20% muscovite. Sulphides occur in laminae. In the XY area it is usually the lowest facies in the section to contain laminated sulphides.									
		- CALCAREOUS MUDSTONE FACIES: Consists of grey to greyish black monotonous, calcareous siliceous carbonaceous mudstone. There are no feathery calcite beds or pyrite-calcite blebs in the facies, making it easily distinguishable from the CCMS.									
		- GRADED LIMESTONE FACIES: Is a laminated argillaceous limestone with intercalated carbonaceous limestone laminae. The main rock type in the facies is laminated limestone with laminae up to 0.1-7mm thick.									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-230

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		- <i>LIGHT GREY BASAL LIMESTONE FACIES - LGLS: Consists of laminated argillaceous limestone. In the Anniv area it marks the end of the ACTM. It's not always present in the stratigraphy.</i> - <i>BASAL FACIES: This is a highly contorted and locally foliated carbonaceous mudstone. Unlike the other facies it is not repeated higher in the member. It appears locally to contain the slip zone of a major slump. The facies has only been observed in the YX area. It is 0.1-2m thick. The facies consists of massive carbonaceous siliceous mudstone with lenses and laminae of contorted, slightly carbonaceous chert.</i> « 69.50- 70.40 Silicious laminated mudstone with decent amounts of sphalerite mineralization. » « 70.40- 73.50 Weakly laminated limestone. No visible mineralization. » « 71.30- 74.00 Dark grey to black silicious mudstone with bits of calcite veining. Some sphalerite visible on laminae. Flt » « 73.50- 74.90 Silicious dark grey to black mudstone with sphalerite mineralization in laminae. Calcite veins and infrequent limestone clasts occur. » « 74.90- 76.50 Coarse light grey limestone with occasional weak laminae, and abundant calcite in thick veins. No visible mineralization. » « 76.50- 79.20 Mixed limestone and calcareous laminated mudstone. Limestone is coarse and massive, light-medium grey. Mudstone is black to dark grey with sphalerite in laminae » « 79.20- 81.10 High grade mineralization in medium grey, silicified mudstone with abundant laminae. Sphalerite occurs in laminations, galena occurs									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-230

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
as veins or infill in small fractures. Visual estimate: Zn: 20-25%, Pb: 10-15% »											
« 81.10- 83.30 Black silicified monotonous mudstone with frequent spidery calcite veins and some limestone clasts. Minor chert banding in last 20cm. No visible mineralization. »											
« 83.30- 83.50 Coarse, internally laminated, light grey limestone. No visible mineralization. Basal limestone. »											
« 83.50- 87.90 Basal limestone transitioning into CCMS, within fault. Variable laminated coarse limestone with some small sections of black silicious mudstone. Calcite occurs in thin distorted stringers and in stylolite-like structures. No visible mineralization. »											
			635318	86.50	88.00	1.50	0.05	0.57	1.00	10.00	0.09
87.90	95.20	FLT	635319	88.00	89.50	1.50	0.38	2.67	1.00	60.00	0.14
« 87.90- 95.20 Slick-n-sides present. Material is CCMS up to 90.9m, and USMS below that. Flt »«Flt gg 10%»« Flt bx 60%»« Brco 10%»			635320	89.50	89.50	0.00	0.01	0.01	1.00	5.00	2.00
			635321	89.50	90.30	0.80	0.16	0.97	1.00	10.00	0.16
			635322	90.30	90.90	0.60	0.25	1.43	2.00	30.00	0.17
			635323	90.90	93.50	2.60	0.06	0.85	1.00	30.00	0.07
			635324	93.50	94.80	1.30	0.12	0.27	1.00	10.00	0.44
			635325	94.80	95.20	0.40	0.55	0.03	3.00	5.00	18.33
95.20	122.50	USMS	635326	95.20	96.60	1.40	0.01	0.01	1.00	5.00	2.00
USMS – Upper Siliceous Mudstone			635327	96.60	98.10	1.50	0.11	0.60	2.00	5.00	0.18
Consists of interlaminated dark grey to black mudstone and light to medium grey chert. Regionally, a 1m thick graptolite zone occurs 15m below the top of the upper unit, this is usable as a horizon. The USMS is divided into 3 units. The Lower Unit contains abundant limestone concretions and Galena and sphalerite micro-concretions occur locally near the base of this unit. « gra , lm chrt -20.00% », « cg xtl sph crns ca 5.00-20.00cm », « bed chrt 10.00-15.00% » « 95.20- 122.40 USMS with some limestone sections. No mineralization present. Calcite veining is typical, silica content is high. Limestone distribution also standard. [Jelle's log from here on] Kate decided to sample			635328	98.10	98.70	0.60	0.01	0.01	1.00	5.00	2.00
			635329	98.70	99.50	0.80	0.08	0.20	1.00	5.00	0.40
			635330	99.50	99.50	0.00	1.37	2.79	18.00	180.00	0.49
			635331	99.50	101.10	1.60	0.13	0.97	1.00	20.00	0.13
			635332	101.10	101.30	0.20	0.07	0.32	1.00	5.00	0.22
			635333	101.30	101.70	0.40	1.02	3.26	1.00	170.00	0.31
			635334	101.70	103.10	1.40	0.01	0.01	1.00	5.00	1.00
			635335	103.10	104.10	1.00	0.01	0.01	1.00	5.00	2.00
			635336	104.10	105.90	1.80	0.01	0.01	1.00	5.00	2.00
			635337	105.90	106.50	0.60	0.01	0.01	1.00	5.00	2.00
			635338	121.20	122.00	0.80	0.12	0.37	1.00	5.00	0.32

Selwyn Project Diamond Drill Log

Hole Number:
XYC-230

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		the USMS. She sampled from 95.2m to 106.5m. The Niton shows very little mineralization, less than 0.6% Zn+Pb, so no detail log or sample of the usms was taken. This unit consists of very silicious (cherty) mudstone. Minor chert bands and some carbonate concretions (some of which show a twinning effect). »	635339	122.00	122.50	0.50	0.01	0.58	1.00	30.00	0.02
122.50	157.80	ACTM	635340	122.50	123.30	0.80	0.57	0.11	1.00	5.00	5.18
		ACTM – Active Member	635341	122.50	123.30	0.80	0.34	0.05	1.00	5.00	6.80
		The ACTM consists of a repetitive, possibly rhythmic, sequence of intercalated carbonaceous mudstone, cherty mudstone, chert and limestone and locally contains economically significant Zn and Pb sulphides (see bold marked facies), mainly in its sections with well developed lamination. Because of its heterogeneity, the member is distinctive and easily identified.	635342	123.30	124.00	0.70	0.13	0.81	1.00	30.00	0.16
		=====	635343	124.00	124.70	0.70	1.28	5.74	2.00	240.00	0.22
		The ACTM has 8 different facies:	635344	124.70	125.40	0.70	2.05	8.23	4.00	340.00	0.25
		=====	635345	125.40	126.10	0.70	1.98	12.22	3.00	490.00	0.16
		- GREY CHERT FACIES: Consists of laminated medium light grey to medium dark grey chert. Mineralization: 95-99% quartz and up to 5% secondary calcite.	635346	126.10	126.50	0.40	11.93	14.42	4.00	900.00	0.83
			635347	126.50	126.90	0.40	11.66	20.36	5.00	1630.00	0.57
		- WHITISH GREY ZN-PB MUDSTONE FACIES: Is a laminated cherty rock containing up to 70% sulphides. Mineralization: quartz, sphalerite and galena are the major minerals with only minor amounts of pyrite and locally calcite. Sedimentary diagenetic structures are common and well displayed in the facies, such as: lamination, pseudo-beds, calcite nodules & limestone nodules and abundant water escape structures. Most obvious structure in facies is cross-cutting veins containing massive sphalerite and galena with minor pyrite. They range in width from 0.5 to 10mm.	635348	126.90	127.40	0.50	12.38	30.02	9.00	2550.00	0.41
			635349	127.40	127.80	0.40	12.01	32.45	7.00	2740.00	0.37
		- THIN BEDDED CHERTY MUDSTONE FACIES: Consists of rhythmic intercalated laminae of chert, carbonaceous mudstone and minor micrite. This facies contains significant amounts of Zn and Pb sulphides.	635350	127.80	127.80	0.00	0.05	0.12	1.00	5.00	0.42
			635351	127.80	128.00	0.20	12.03	30.76	6.00	2600.00	0.39
			635352	128.00	128.30	0.30	11.53	15.70	5.00	1300.00	0.73
			635353	128.30	128.90	0.60	8.89	18.27	5.00	1400.00	0.49
			635354	128.90	129.90	1.00	1.51	4.92	1.00	150.00	0.31
			635355	129.90	130.20	0.30	7.63	18.30	5.00	730.00	0.42
			635356	130.20	130.70	0.50	0.66	1.42	1.00	50.00	0.46
			635357	130.70	131.60	0.90	0.37	1.41	1.00	50.00	0.26
			635358	131.60	132.60	1.00	0.55	1.48	1.00	50.00	0.37
			635359	132.60	133.70	1.10	0.43	2.36	1.00	80.00	0.18
			635360	133.70	133.70	0.00	5.96	6.65	70.00	190.00	0.90
			635361	133.70	134.60	0.90	0.33	0.08	1.00	5.00	4.13
			635362	134.60	135.20	0.60	4.06	9.64	2.00	320.00	0.42
			635363	135.20	135.90	0.70	0.13	0.51	1.00	20.00	0.25
			635364	135.90	137.00	1.10	1.49	4.46	1.00	130.00	0.33
			635365	137.00	137.70	0.70	0.94	2.09	5.00	50.00	0.45
			635366	137.70	138.10	0.40	4.38	16.91	1.00	670.00	0.26
			635367	138.10	138.50	0.40	1.40	26.00	3.00	770.00	0.05

Selwyn Project Diamond Drill Log

Hole Number:
XYC-230

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
- CHERTY MUDSTONE FACIES: Consists of a greyish black monotonous siliceous, carbonaceous mudstone. It is most typically found overlying the thin bedded calcareous mudstone facies. - THIN BEDDED CALCAREOUS MUDSTONE FACIES: Consists of laminated carbonaceous mudstone containing 20-40% calcite, 40-55% quartz and 10-20% muscovite. Sulphides occur in laminae. In the XY area it is usually the lowest facies in the section to contain laminated sulphides. - CALCAREOUS MUDSTONE FACIES: Consists of grey to greyish black monotonous, calcareous siliceous carbonaceous mudstone. There are no feathery calcite beds or pyrite-calcite blebs in the facies, making it easily distinguishable from the CCMS. - GRADED LIMESTONE FACIES: Is a laminated argillaceous limestone with intercalated carbonaceous limestone laminae. The main rock type in the facies is laminated limestone with laminae up to 0.1-7mm thick. - LIGHT GREY BASAL LIMESTONE FACIES - LGLS: Consists of laminated argillaceous limestone. In the Anniv area it marks the end of the ACTM. It's not always present in the stratigraphy. - BASAL FACIES: This is a highly contorted and locally foliated carbonaceous mudstone. Unlike the other facies it is not repeated higher in the member. It appears locally to contain the slip zone of a major slump. The facies has only been observed in the YX area. It is 0.1-2m thick. The facies consists of massive carbonaceous siliceous mudstone with lenses and laminae of contorted, slightly carbonaceous chert. « 122.50- 124.00 Very silicious (cherty) mudstone. Could still be part of USMS. Visible galena at the top of the range. »			635368	138.50	138.90	0.40	0.73	2.54	2.00	70.00	0.29
			635369	138.90	139.50	0.60	1.75	6.32	1.00	190.00	0.28
			635370	139.50	140.30	0.80	0.53	1.15	1.00	30.00	0.46
			635371	139.50	140.30	0.80	0.27	1.30	1.00	30.00	0.21
			635372	140.30	140.80	0.50	6.86	39.48	10.00	920.00	0.17
			635373	140.80	141.50	0.70	4.63	16.73	4.00	410.00	0.28
			635374	141.50	142.30	0.80	1.02	1.99	1.00	50.00	0.51
			635375	142.30	143.00	0.70	0.53	3.25	1.00	80.00	0.16
			635376	143.00	144.00	1.00	0.12	0.33	1.00	5.00	0.36
			635377	144.00	144.90	0.90	0.03	0.13	1.00	5.00	0.23
			635378	144.90	146.30	1.40	0.06	0.03	1.00	5.00	2.00
			635379	146.30	147.90	1.60	0.10	0.07	1.00	5.00	1.43
			635380	147.90	147.90	0.00	0.01	0.01	1.00	5.00	2.00
			635381	147.90	149.00	1.10	0.31	1.66	1.00	40.00	0.19
			635382	149.00	150.40	1.40	0.12	0.54	1.00	10.00	0.22
			635383	150.40	152.00	1.60	0.21	0.83	3.00	20.00	0.25
			635384	152.00	153.50	1.50	0.15	1.33	4.00	40.00	0.11
			635385	153.50	155.10	1.60	0.24	0.31	5.00	5.00	0.77
			635386	155.10	156.40	1.30	0.01	0.01	2.00	5.00	2.00
			635387	156.40	157.00	0.60	0.01	0.01	1.00	5.00	2.00
			635388	157.00	157.80	0.80	0.01	0.01	1.00	5.00	2.00

Selwyn Project Diamond Drill Log

Hole Number:
XYC-230

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		« 124.00- 125.40 Silicious mudstone with a moderately to well developed lamination. Zn: 7%; Pb: 4% »									
		« 125.40- 126.10 Silicious mudstone with well developed laminations. Zn: 10%; Pb: 3% »									
		« 126.10- 128.90 High grade mineralization. Whitish grey mudstone facies. >30% combined Zn and Pb. »									
		« 128.90- 129.90 Silicious mudstone with a moderately developed lamination. One limestone clast. Zn: 4%; Pb: 1%. »									
		« 129.90- 130.20 High grade mineralization. >20% Zn+Pb »									
		« 130.20- 130.70 Faintly calcareous mudstone with poorly developed lamination, and limestone. +/- 2% Zn & Pb »									
		« 130.70- 134.60 Mainly silicious mudstone with no lamination. Mineralization <1% Zn+Pb »									
		« 134.60- 135.20 Silicious mudstone with moderately developed lamination and some limestone. Zn: 8%, Pb: 5% »									
		« 135.20- 135.90 Calcite vein, barren. »									
		« 135.90- 137.70 Limestone and calcareous mudstone with poorly developed lamination. Zn: 3%, Pb: 1% »									
		« 137.70- 138.50 High grade mineralization. Calcareous mudstone, very rich in sphalerite and galena. Zn+ Pb: 30% »									
		« 138.50- 138.90 Limestone with minor mineralization. Zn: 1.5%; Pb: 1% »									
		« 138.90- 139.50 Calcareous mudstone with moderately developed									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-230

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		lamination. Zn: 5%, Pb: 2.5%. Five cm of high-grade at the end. » « 139.50- 140.30 Limestone and calcareous mudstone with minor to no lamination. <2% Zn +Pb » « 140.30- 141.50 High grade mineralization. Whitish-grey Zn-Pb. Mudstone facies. >20% Zn +Pb » « 141.50- 150.40 Mainly calcareous mudstone and limestone. <1% Zn+Pb » « 150.40- 155.10 Carbonaceous silicious mudstone. Barren. Contains minor amount of a mineral that has trace amounts of Ni (0.22%), V(0.52%) » « 155.10- 157.80 Basal light grey limestone with more of that mineral in previous interval. »									
157.80	176.00	CCMS	635389	157.80	158.60	0.80	0.01	0.01	4.00	5.00	2.00
		CCMS – Calcareous Mudstone	635390	158.60	158.60	0.00	1.40	2.97	20.00	180.00	0.47
			635391	158.60	159.70	1.10	0.04	0.86	5.00	50.00	0.05
		Massive, calcareous, carbonaceous, dark grey mudstone. Most of the member is massive, but rare poorly defined bedding and pyrite-calcite micro-concretions are present. Most diagnostic structures are feathery calcite beds (=thin calcite-cemented concretions, many of them contain pyrite cores) and calcite pseudo-beds (= fibrous calcite vein parallel to bedding). « lm ca 5.00-10.00mm », « nodules py -3.00% 2.00-20.00mm » < @ 168.00 S0 defined by faint pyrite beds. S0 tca 70° > < @ 168.30 S0 defined by faint pyrite beds. S0 tca 69° > < @ 175.90 S0 defined by faint pyrite beds. S0 tca 72° >									
176.00	176.00	EOH									

Diamond Drill Log

Comprehensive Report for Hole:

XYC-229

Hole No.: XYC-229	Depth: 236.00 m	Horizontal Length: 0.00 m	Project: 1710
Location Data:			
Property:	Selwyn Project	Claim Name:	X 14
Mining District:	Selwyn Basin	Grant Number:	Y 64539
Province/Territory:	Yukon		
UTM Co-Ordinates & Altitude of Drill Hole Collar:			
UTM Easting:	488768.89 m	True Azimuth:	210.0 °
UTM Northing:	6926229.19 m	Hole Angle:	-70.0 °
Elevation (m):	1583.82 m	NTS Name:	Placer Creek
		NTS Number:	105I06
Grid Co-Ordinates of Drill Hole Collar:			
Grid Easting (m):	0.00 m	Grid Name:	HP 06
Grid Northing (m):	0.00 m	Grid Type:	100m
Grid Azimuth:	270.0 °		
Dimond Drilling Contract:			
Drilled By:	CY-02	Date Drilling Start:	10/13/2010
		Date Finish:	10/15/2010
Diamond Drill Core:			
Logged By:	Kate Cameron	Date Logging Start:	10/19/2010
		Date Finish:	10/20/2010
Legend for Core Logging Codes: PAX			
Core Size:	NQ	Cemented:	Yes
Casing Depth:	15.00 m	Casing Pulled:	Yes
Water Depth:	0.00 m	Overburden Depth:	15.00 m
Level:	Section:	Drift:	

Selwyn Project

Diamond Drill Log

Survey Data for Hole

XYC-229

Hole Comments:

Wed, Oct 13 ---XYC-226 was shut down at 125.8m in CCMS, the drill moved to set up #60. At this new set up they are at 10.5m still driving casing, going through sandy section that keeps caving in.

=====

Thu, Oct 14 --- Total depth of 110m in USMS. 15m casing. 10-15cm zone of weak mineralization at 24m.

=====

Fri, Oct 15 --- At 191 meters with no ACTM intersection as yet. Confirmed USMS to 127.5m, followed by a 15m fault with small pieces of hard to identify m/s. Another fault from 169-177m. We could be in CCMS, or USMS at this point, there were a few chert banks in the last few meters this morning lending the possibility to USMS. We will continue to drill.

=====

Sat, Oct 16 --- XYC-229 was shut down yesterday evening at 237m in Transition formation. Greg is currently having the drill spun around to drill target #59. This will be XYC-230.

<i>Depth</i>	<i>Dip</i>	<i>Azimuth</i>
0.00	-70.0	210.0
50.00	-69.7	209.3
110.00	-69.1	209.5
152.00	-68.3	207.4
203.00	-66.4	205.8
236.00	-65.7	204.8

Selwyn Project Diamond Drill Log

Hole Number:
XYC-229

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
0.00	15.00	OVBR									
15.00	127.50	USMS									
USMS – Upper Siliceous Mudstone											
Consists of interlaminated dark grey to black mudstone and light to medium grey chert. Regionally, a 1m thick graptolite zone occurs 15m below the top of the upper unit, this is usable as a horizon. The USMS is divided into 3 units. The Lower Unit contains abundant limestone concretions and Galena and sphalerite micro-concretions occur locally near the base of this unit. « gra , lm chrt -20.00% », « cg xtl sph crns ca 5.00-20.00cm », « bed chrt 10.00-15.00% »,											
Typical Upper Siliceous. Dark grey to black mudstone with lighter grey chert bands that can be both planar and wormy. Calcite veins are mostly thin, irregular stringers, also occasional 0.5-2cm distorted veins.											
Pyrite occurs with calcite veins and disseminated in bands or blebs 1 to 10mm long.											
Some sections of limestone less than 1m wide. They do not have the radial structure one would expect from concretions. Some are coarse grained and massive, other are finer grained and have internal lamination somewhat conformable to the host mudstone. Fissile rock. Graphitic.											
« 15.00- 20.70 Zone at top of hole is very broken up BRKN »											
« 21.40- 22.60 FLT »« flt bx 10%»« flt gg 90%»											
« 45.00- 68.10 FLT »« brkn core 70%»« flt bx 20%»« flt gg 10%»											
« 74.00- 98.50 Several faults, large zone of breakage FLT »« brkn core 10%»« flt bx 40%»« flt gg 15%»											
« 103.00- 112.50 Several faults, large zone of breakage. Slicken slides											

Selwyn Project Diamond Drill Log

Hole Number:
XYC-229

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		FLT »« brkn core 10%»« flt bx 35%»« flt gg 15%» « 118.10- 128.10 Several faults in large zone of breakage. Slicken slides FLT »« brkn core 40%»« flt bx 30%»« flt gg » < @ 119.10 One small bleb of galena in a vein with calcite Galena > < @ 124.30 Bx. Mdst fragments hosted in coarse lmst. Frags are angular, 0.25-8cm Bx >									
127.50	146.00	FLT									
		Slicken slides are present. Much of the gouge is re-constituted into slightly competent core. Whole core 20% - Broken core 20% - Breccia 40% - Gouge 20%. Whole core is broken mechanically from drilling process because it is so highly fissile. This fault causes the lithology to jump from Upper Siliceous to CCMS.									
146.00	216.90	CCMS									
		CCMS – Calcareous Mudstone Massive, calcareous, carbonaceous, dark grey mudstone. Most of the member is massive, but rare poorly defined bedding and pyrite-calcite micro-concretions are present. Most diagnostic structures are feathery calcite beds (=thin calcite-cemented concretions, many of them contain pyrite cores) and calcite pseudo-beds (= fibrous calcite vein parallel to bedding). « lm ca 5.00-10.00mm », « nodules py -3.00% 2.00-20.00mm », Badly faulted. Disseminated pyrite beds, wispy calcite stringers. Carbonaceous. « 146.00- 166.50 Very Fissile core. Abundant mechanical breakage BRKN » « 166.50- 177.90 Slicken slides present FLT »« brkn core 10%»« flt bx 40%»« flt gg 20%» « 191.90- 199.80 Slicken Slides present FLT »« brkn core 30%»« flt bx 40%»« flt gg 10%»									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-229

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		< @ 203.80 10cm of pure gouge. Approx 30cm of core last FLT > < @ 211.40 15cm of gouge and breccia FLT > < @ 211.40 ft bx 50% > < @ 211.40 ft gg 50% >									
216.90	217.40	FLT Reconstituted breccia and gouge is now fairly solid core. CCMS. lost, skips to Transition Unit.									
217.40	236.00	TRAN TRAN – Transition Formation Consists of laminated tan mudstone and minor intercalated light grey limestone. « lm mdst 1.00-10.00mm » Siliceous, fine, slightly wavy laminae. Medium grey, very little calcite veining. « 230.00- 234.50 Minor pyrite blebs with calcite 2mm - 1.5cm » « 234.50- 236.00 Frequent pyrite blebs with calcite 1cm - 10cm, very irregular shape. » < @ 235.10 Fine, wavy laminae S0 tca 25° >									
236.00	236.00	EOH									

Diamond Drill Log

Comprehensive Report for Hole:

XYC-228

Hole No.: XYC-228	Depth: 231.20 m	Horizontal Length: 0.00 m	Project: 1710
Location Data:			
Property:	Selywn Project	Claim Name:	X 13
Mining District:	Selwyn Basin	Grant Number:	Y 64538
Province/Territory:	Yukon		
UTM Co-Ordinates & Altitude of Drill Hole Collar:			
UTM Easting:	488801.06 m	True Azimuth:	215.0 °
UTM Northing:	6926401.39 m	Hole Angle:	-85.0 °
Elevation (m):	1639.74 m	NTS Name:	Placer Creek
		NTS Number:	105I06
Grid Co-Ordinates of Drill Hole Collar:			
Grid Easting (m):	0.00 m	Grid Name:	HP 06
Grid Northing (m):	0.00 m	Grid Type:	100m
Grid Azimuth:	275.0 °		
Dimond Drilling Contract:			
Drilled By:	CY-01	Date Drilling Start:	10/12/2010
		Date Finish:	10/16/2010
Diamond Drill Core:			
Logged By:	Kate Cameron	Date Logging Start:	10/30/2010
		Date Finish:	11/03/2010
Legend for Core Logging Codes: PAX			
Core Size:	NQ/NQ3	Cemented:	Yes
Casing Depth:	9.80 m	Casing Pulled:	Yes
Water Depth:	0.00 m	Overburden Depth:	9.80 m
Level:	Section:	Drift:	

Selywn Project

Diamond Drill Log

Survey Data for Hole

XYC-228

Hole Comments:

Wed, Oct 13 ---XYC-224 was shut down and moved to set up #13 yesterday. Curently XYC-228 is at set up #13 at a total depth of 98m in FLMD. They passed through a fault between 86-93m.

=====

Thu, Oct 14 --- Total depth of 147.2m in USMS. FLMD-USMS contact at 100m. 10-15cm zone of weak mineralization at 107.5m.

=====

Fri, Oct 15 --- "At 195.2m in ACTM. USMS - ACTM contact at 186m. Very blocky core with poor recovery."

=====

Sat, Oct 16 --- XYC-228 was shut down this morning in CCMS at 231.2m. ACTM-CCMS contact at 207m. The are moving to target number 54 right now, which will become XYC-232.

<i>Depth</i>	<i>Dip</i>	<i>Azimuth</i>
0.00	-85.0	215.0
50.00	-84.9	214.2
101.00	-84.2	213.4
150.20	-83.7	207.6
201.20	-82.8	205.8
231.20	-82.9	211.5

Selwyn Project Diamond Drill Log

Hole Number:
XYC-228

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
0.00	9.80	OVBR									
9.80	99.00	FLMD									
FLMD – Flaggy Mudstone Formation											
Dark grey mudstone in the upper portions of the unit grading into light grey mudstone to siltstone. Contains abundant wispy bioturbation which ranges from randomly-oriented at the top of the unit to bedding-parallel throughout the majority of the unit. Darker upper section has a strong fetid odour along broken surfaces. « btrb 0.10-2.00cm », « cg xtl crns ca 1.00-5.00% 5.00-150.00cm », « crns py 1.00-5.00% 0.10-0.50mm », Frequent sections near top are broken zones not worth logging individually. « 9.80- 34.00 Near surface wx and breakage Broken Zone »« flt gg 5%»« flt bx 75%»« brkn core 10%» ◁ @ 45.00 Defined by bioturbations S0 tca 55° ▷ ◁ @ 51.90 Defined by ca veins S0 tca 20° ▷ « 72.80- 78.20 FLT »« flt gg 10%»« flt bx 75%»« brkn core 10%» ◁ @ 80.10 Defined by bioturbations S0 tca 30° ▷ « 86.10- 93.70 FLT »« flt gg 10%»« flt bx 75%»« brkn core 10%»											
99.00	186.20	USMS	633801	182.50	185.60	3.10	0.01	0.12	1.00	5.00	0.08
USMS – Upper Siliceous Mudstone			633802	185.60	186.00	0.40	0.41	0.64	1.00	30.00	0.64
			633803	186.00	186.20	0.20	0.01	0.17	1.00	5.00	0.06
Consists of interlaminated dark grey to black mudstone and light to medium grey chert. Regionally, a 1m thick graptolite zone occurs 15m below the top of the upper unit, this is usable as a horizon. The USMS is divided into 3 units. The Lower Unit contains abundant limestone concretions and Galena and sphalerite											

Selwyn Project Diamond Drill Log

Hole Number:
XYC-228

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
micro-concretions occur locally near the base of this unit. « gra , lm chrt -20.00% », « cg xtl sph crns ca 5.00-20.00cm », « bed chrt 10.00-15.00% », Typical, competent, highly siliceous. « 99.30- 100.60 FLT »« flt gg 15%»« flt bx 35%»« brkn core 50%» < @ 104.30 Defined by wormy chert bands S0 tca 70° > < @ 118.70 Defined in parallel chert bands S0 tca 55° > « 147.80- 147.90 Small zone of sph lamination. Lams are fine, parallel and have been distorted by moderate minor faulting » < @ 172.70 In parallel thin chert bands, discrete layers or disseminated py and ca veins S0 tca 75° > « 184.20- 186.20 FLT »											
186.20	207.30	ACTM	633804	186.20	187.40	1.20	6.01	9.75	3.00	490.00	0.62
ACTM – Active Member			633805	187.40	188.10	0.70	0.92	4.06	1.00	120.00	0.23
			633806	188.10	191.80	3.70	0.97	4.39	1.00	110.00	0.22
The ACTM consists of a repetitive, possibly rhythmic, sequence of intercalated carbonaceous mudstone, cherty mudstone, chert and limestone and locally contains economically significant Zn and Pb sulphides (see bold marked facies), mainly in its sections with well developed lamination. Because of its heterogeneity, the member is distinctive and easily identified.			633807	191.80	192.00	0.20	0.07	0.43	1.00	5.00	0.16
			633808	192.00	192.50	0.50	0.07	1.21	1.00	30.00	0.06
			633809	192.50	197.60	5.10	3.64	2.61	1.00	80.00	1.39
			633810	197.60	198.80	1.20	2.43	6.22	1.00	230.00	0.39
			633811	197.60	198.80	1.20	1.06	3.84	1.00	110.00	0.28
			633812	198.80	199.50	0.70	0.19	0.77	1.00	20.00	0.25
=====			633813	199.50	200.10	0.60	0.07	0.19	1.00	5.00	0.37
The ACTM has 8 different facies:			633814	200.10	201.20	1.10	0.27	1.64	2.00	40.00	0.16
=====			633815	201.20	202.70	1.50	0.56	0.74	4.00	20.00	0.76
			633816	202.70	203.60	0.90	0.19	1.11	5.00	30.00	0.17
- GREY CHERT FACIES: Consists of laminated medium light grey to medium dark grey chert. Mineralization: 95-99% quartz and up to 5% secondary calcite.			633817	203.60	204.40	0.80	0.64	0.58	5.00	20.00	1.10
			633818	204.40	204.60	0.20	2.43	0.20	11.00	5.00	12.15

Selwyn Project Diamond Drill Log

Hole Number:
XYC-228

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
- WHITISH GREY ZN-PB MUDSTONE FACIES: Is a laminated cherty rock containing up to 70% sulphides. Mineralization: quartz, sphalerite and galena are the major minerals with only minor amounts of pyrite and locally calcite. Sedimentary diagenetic structures are common and well displayed in the facies, such as: lamination, pseudo-beds, calcite nodules & limestone nodules and abundant water escape structures. Most obvious structure in facies is cross-cutting veins containing massive sphalerite and galena with minor pyrite. They range in width from 0.5 to 10mm. - THIN BEDDED CHERTY MUDSTONE FACIES: Consists of rhythmic intercalated laminae of chert, carbonaceous mudstone and minor micrite. This facies contains significant amounts of Zn and Pb sulphides. - CHERTY MUDSTONE FACIES: Consists of a greyish black monotonous siliceous, carbonaceous mudstone. It is most typically found overlying the thin bedded calcareous mudstone facies. - THIN BEDDED CALCAREOUS MUDSTONE FACIES: Consists of laminated carbonaceous mudstone containing 20-40% calcite, 40-55% quartz and 10-20% muscovite. Sulphides occur in laminae. In the XY area it is usually the lowest facies in the section to contain laminated sulphides. - CALCAREOUS MUDSTONE FACIES: Consists of grey to greyish black monotonous, calcareous siliceous carbonaceous mudstone. There are no feathery calcite beds or pyrite-calcite blebs in the facies, making it easily distinguishable from the CCMS. - GRADED LIMESTONE FACIES: Is a laminated argillaceous limestone with intercalated carbonaceous limestone laminae. The main rock type in the facies is laminated limestone with laminae up to 0.1-7mm thick. - LIGHT GREY BASAL LIMESTONE FACIES - LGLS: Consists of laminated			633819	204.60	205.90	1.30	0.03	0.01	1.00	5.00	6.00
			633820	205.90	205.90	0.00	0.01	0.01	1.00	5.00	2.00
			633821	205.90	207.30	1.40	0.01	0.01	1.00	5.00	2.00

Selwyn Project Diamond Drill Log

Hole Number:
XYC-228

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		argillaceous limestone. In the Anniv area it marks the end of the ACTM. It's not always present in the stratigraphy. - BASAL FACIES: This is a highly contorted and locally foliated carbonaceous mudstone. Unlike the other facies it is not repeated higher in the member. It appears locally to contain the slip zone of a major slump. The facies has only been observed in the YX area. It is 0.1-2m thick. The facies consists of massive carbonaceous siliceous mudstone with lenses and laminae of contorted, slightly carbonaceous chert. Typical, though short intersection, nothing high grade or out of the ordinary. « 186.20- 187.40 Med grey si_mdst with abundant sph lams. Most of section has been turned in the drill and/or lost. Mod-good grade » « 187.40- 191.80 Dk grey, sph lams, si_mdst with abundant ca/py veins. Niton 1.66% Pb, 3.42% Zn » « 188.10- 188.90 10cm recovered FLT »« flt gg 50%»« flt bx 50%» « 191.80- 192.00 Coarse lt-med grey lmst. Massive, monotonous » « 192.00- 197.60 Graphitic Si sph lam mdst. Dk grey to black. Niton 1.95% Pb, 5.5% Zn » « 192.50- 197.60 FLT »« flt gg 10%»« flt bx 40%»« brkn core 25%» « 197.60- 200.10 Med-lt grey calc mdst and lmst clasts or concretions. Well broken unit. No visible mnx » « 200.10- 201.20 Graphitic, si, dk grey to black mdst. Weak ca veining. No visible mnx »									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-228

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		« 200.30- 200.70 10cm recovered FLT »« flt gg 20%»« flt bx 80%»									
		« 201.20- 202.70 As last, with more graphite and ca veins. Very fissile and crumbly »									
		« 202.70- 204.60 As 200.1, with slightly increase ca stringers. Competent. »									
		« @ 204.50 10cm at interface between mdst and basal lmst where ga occurs in blebs »									
		« 204.60- 207.30 Basal lmst. Lt grey, f.g. Weakly laminated, few ca veins. Competent »									
207.30	231.20	CCMS	633822	207.30	208.60	1.30	0.01	0.01	2.00	5.00	2.00
		CCMS – Calcareous Mudstone	633823	208.60	208.60	0.00	1.44	2.95	16.00	180.00	0.49
		Massive, calcareous, carbonaceous, dark grey mudstone. Most of the member is massive, but rare poorly defined bedding and pyrite-calcite micro-concretions are present. Most diagnostic structures are feathery calcite beds (=thin calcite-cemented concretions, many of them contain pyrite cores) and calcite pseudo-beds (= fibrous calcite vein parallel to bedding).									
		« lm ca 5.00-10.00mm », « nodules py -3.00% 2.00-20.00mm »,									
		Typical. Barren, monotonous, black massive mdst. Stylolites present. Bands of disseminated ca/py present.									
		« @ 214.40 Defined by disseminated ca/py veins S0 tca 75% »									
231.20	231.20	EOH									

Diamond Drill Log

Comprehensive Report for Hole:

XYC-227

Hole No.: XYC-227	Depth: 114.00 m	Horizontal Length: 0.00 m	Project: 1710
Location Data:			
Property:	Selwyn Project	Claim Name:	X 13
Mining District:	Selwyn Basin	Grant Number:	Y 64538
Province/Territory:	Yukon		
UTM Co-Ordinates & Altitude of Drill Hole Collar:			
UTM Easting:	488662.90 m	True Azimuth:	210.0 °
UTM Northing:	6926458.63 m	Hole Angle:	-83.0 °
Elevation (m):	1625.76 m	NTS Name:	Placer Creek
		NTS Number:	105L06
Grid Co-Ordinates of Drill Hole Collar:			
Grid Easting (m):	0.00 m	Grid Name:	HP 06
Grid Northing (m):	0.00 m	Grid Type:	100m
Grid Azimuth:	270.0 °		
Dimond Drilling Contract:			
Drilled By:	NL-01	Date Drilling Start:	10/10/2010
		Date Finish:	10/15/2010
Diamond Drill Core:			
Logged By:	Kate Cameron	Date Logging Start:	10/19/2010
		Date Finish:	
Legend for Core Logging Codes: PAX			
Core Size:	NQ	Cemented:	Yes
Casing Depth:	9.60 m	Casing Pulled:	Yes
Water Depth:	0.00 m	Overburden Depth:	9.60 m
Level:	Section:	Drift:	

Selwyn Project

Diamond Drill Log

Survey Data for Hole

XYC-227

Hole Comments:

Mon, Oct 11 ---Moved to set up #14 (XYC-227) yesterday where casing gotted jammed at 4 feet. Nightshift tried cutting the casing and re-angled it. At 30 feet of casing they hit a clay horizon and dropped the crown. No core from this drill. The new dip of XYC-227 is -82.5 degrees.

=====

Tue, Oct 12 --- At a total depth of 33mm. 0-9.8m CAS; 9.8m - 18m BSSM; 18m-33m FLMD.

=====

Wed, Oct 13 ---At a total depth of 107.6m in FLMD.

=====

Thu, Oct 14 --- Drill on standby, still at 107.6m. Nightshift driller evacuated yesterday for medical concerns, helper sent home. Dayshift driller and helper left for break yesterday. Only one plane could land, NL-01 cross shift was not on it.

=====

Fri, Oct 15 --- Yesterday dayshift arrived at noon, and prepped the drill in the afternoon, but did not produce any core. There is currently no nightshift for this drill.

<i>Depth</i>	<i>Dip</i>	<i>Azimuth</i>
0.00	-83.0	210.0
57.00	-70.5	207.8

Selwyn Project Diamond Drill Log

Hole Number:
XYC-227

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
0.00	9.60	OVBR									
9.60	17.90	BSSM									
<i>BSSM – Backside Siliceous Mudstone</i> <i>Devonian Siliceous Mudstone – Upper Chert Formation</i> <i>Greyish black laminated chert and siliceous mudstone. Randomly-oriented to bedding-parallel bioturbation is common in the bottom of the unit. « lm chrt 75.00-95.00% », « btrb 0.10-2.00cm »</i> <i>« 9.60- 17.90 Unit is fairly broken up, being near surface. Dark grey-black, looks somewhat like CCMS. Monotonous. Infrequent pyrite blebs. Carbonaceous. »</i> <i>« 9.90- 14.10 Frequent 2-4mm slightly wormy calcite veins- calcareous section. »</i> <i>< @ 13.70 S0 tca 55° ></i>											
17.90	97.30	FLMD									
<i>FLMD – Flaggy Mudstone Formation</i> <i>Dark grey mudstone in the upper portions of the unit grading into light grey mudstone to siltstone. Contains abundant wispy bioturbation which ranges from randomly-oriented at the top of the unit to bedding-parallel throughout the majority of the unit. Darker upper section has a strong fetid odour along broken surfaces. « btrb 0.10-2.00cm », « cg xtl crns ca 1.00-5.00% 5.00-150.00cm », « crns py 1.00-5.00% 0.10-0.50mm »</i> <i>« 17.90- 97.30 Typical flaggy mudstone. Light grey with darker grey sections. Abundant bioturbations. Competent rock. Few calcite veins/stringers. Bedding is very difficult to measure. »</i> <i>« 22.10- 24.00 Worst breakage/breccia is at the top of fault; pieces get bigger downhole. FLT »« Flt gg 10%»« Flt bx 40%»« Brco 50%»</i>											

Selwyn Project Diamond Drill Log

Hole Number:
XYC-227

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		« 24.00- 25.10 Broken zone. Could be largely mechanical breakage along abundant planes of weakness caused by overlying fault. » ◁ @ 25.20 S0 measured along roughly parallel but distorted/bioturbated beds. S0 tca 60° ▷ ◁ @ 28.10 S0 defined by bioturbated beds. S0 tca 20° ▷ ◁ @ 36.40 S0 defined by bioturbated beds. S0 tca 15-20° ▷ « 39.10- 40.10 Black mudstone section. Sharp contacts. Remincent of CCMS, with tiny feathery calcite stringers, bands of disseminated pyrite, and calcite/pyrite beds. » « 40.40- 41.30 Black mudstone as at 39.1m. » ◁ @ 42.00 S0 defined by fine, dark grey, weakly "bioturbated" laminae. S0 tca 55° ▷ « 42.16- 46.00 Darker grey than the rest of the unit. "Bioturbation" weak to zero. Laminae are faint, fine, and parallel. Calcareous. » ◁ @ 45.00 S0 defined by faint, fine laminae. S0 tca 45-50° ▷ « 46.00- 47.50 Faint but 2-5cm wormy medium grey chert bands, in silicious black monotonous mudstone. » ◁ @ 48.00 S0 in dark grey "bioturbated" beds. S0 tca 25° ▷ ◁ @ 59.80 S0 in dark grey "bioturbated" beds. S0 tca 25° ▷ ◁ @ 68.60 S0 in dark grey "bioturbated" beds. S0 tca 30° ▷ « 71.10- 72.40 Slightly darker section, dark grey to black. » ◁ @ 87.10 S0 in "bioturbated" beds. S0 tca 25° ▷ « 92.00- 94.30 Flaggy-ness weakens and unit is dark grey. »									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-227

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		« 95.50- 97.30 Bottom of unit is calcic. »									
97.30	114.00	USMS USMS – Upper Siliceous Mudstone Consists of interlaminated dark grey to black mudstone and light to medium grey chert. Regionally, a 1m thick graptolite zone occurs 15m below the top of the upper unit, this is usable as a horizon. The USMS is divided into 3 units. The Lower Unit contains abundant limestone concretions and Galena and sphalerite micro-concretions occur locally near the base of this unit. « gra , lm chrt -20.00% », « cg xtl sph crns ca 5.00-20.00cm », « bed chrt 10.00-15.00% » « 97.30- 113.00 Non-typical USMS. Rock is mostly monotonous, black. Fewer chert bands than normal, less fracturing, fewer calcite veins. Some sections are highly calcareous- these cannot be distinguished by eye, they must be tested with HCL. Occasional pyrite with calcite. Weak planar lamination. » < @ 102.80 S0 shown by very thin calcite stringers and minute changes in tone of grey. S0 tca 50° >									
114.00	114.00	EOH									

Selwyn Project

Diamond Drill Log

Comprehensive Report for Hole:

XYC-226

Hole No.: XYC-226	Depth: 125.80 m	Horizontal Length: 0.00 m	Project: 1710
Location Data:			
Property:	Selwyn Project	Claim Name:	X 11
Mining District:	Selwyn Basin	Grant Number:	Y 64536
Province/Territory:	Yukon		
UTM Co-Ordinates & Altitude of Drill Hole Collar:			
UTM Easting:	488549.00 m	True Azimuth:	204.0 °
UTM Northing:	6926387.00 m	Hole Angle:	-84.0 °
Elevation (m):	1568.00 m	NTS Name:	Placer Creek
		NTS Number:	105L06
Grid Co-Ordinates of Drill Hole Collar:			
Grid Easting (m):	0.00 m	Grid Name:	HP 06
Grid Northing (m):	0.00 m	Grid Type:	100m
Grid Azimuth:	264.0 °		
Dimond Drilling Contract:			
Drilled By:	CY-02	Date Drilling Start:	10/10/2010
		Date Finish:	10/12/2010
Diamond Drill Core:			
Logged By:	Kate Cameron / Graham	Date Logging Start:	10/30/2010
		Date Finish:	
Legend for Core Logging Codes: PAX			
Core Size:	NQ/NQ3	Cemented:	Yes
Casing Depth:	12.90 m	Casing Pulled:	Yes
Water Depth:	0.00 m	Overburden Depth:	12.90 m
Level:			
Section:		Drift:	

Selwyn Project

Diamond Drill Log

Survey Data for Hole

XYC-226

Hole Comments:

Sun, Oct 10 --- XYC-222 got shut down yesterday at 147m, and moved to set-up #18. At new set-up, 12.2m of casing and currently at 14m down in USMS. Drill had issues with hydraulic cooler.

=====

Mon, Oct 11 ---Total depth of 80m. Still in USMS. Apparently their pad has melt-settled slightly so they are a little offline, but it is still easily drillable.

=====

Tue, Oct 12 --- Drill shut down at a total depth of 125.8m at midnight in CCMS. They were in a fault they could not pass. Last ACTM was at ~115m. The new pad is being cleared this morning and they will move this afternoon.

<i>Depth</i>	<i>Dip</i>	<i>Azimuth</i>
0.00	-84.0	204.0
56.00	-83.6	200.4
100.20	-83.3	205.1
124.20	-83.1	203.4

Selwyn Project Diamond Drill Log

Hole Number:
XYC-226

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
0.00	12.90	OVBR									
12.90	97.10	USMS	634001	94.20	95.00	0.80	0.02	0.09	1.00	5.00	0.22
USMS – Upper Siliceous Mudstone			634002	95.00	97.10	2.10	0.02	0.36	1.00	10.00	0.06
Consists of interlaminated dark grey to black mudstone and light to medium grey chert. Regionally, a 1m thick graptolite zone occurs 15m below the top of the upper unit, this is usable as a horizon. The USMS is divided into 3 units. The Lower Unit contains abundant limestone concretions and Galena and sphalerite micro-concretions occur locally near the base of this unit. « gra , lm chrt -20.00% », « cg xtl sph crns ca 5.00-20.00cm », « bed chrt 10.00-15.00% »											
◁ @ 22.80 S0 defined by cherty bands. S0 tca 45° ▷											
« 26.30- 28.80 FLT »« Flt gg 35%»« Flt bx 30%»« Brco 35%»											
« 35.00- 41.00 FLT »« Flt gg 15%»« Flt bx 75%»« Brco 10%»											
« 44.10- 44.50 FLT »« Flt gg 70%»« Flt bx 30%»											
◁ @ 48.00 S0 defined by cherty bands. S0 tca 50° ▷											
◁ @ 59.20 S0 defined by cherty bands. S0 tca 25° ▷											
◁ @ 74.70 S0 defined by cherty bands. S0 tca 30° ▷											
« 79.20- 97.10 Not typical USMS. Recrystallized qt and calcite veins are on average larger than typical USMS, also more calcite-qt veinlet swarms associated with larger veins. Massive pyrite can form pseudo-laminae- often intruded upon by qt-calcite. In general the rock is dark grey, silicious, poorly laminated, ~2% cal-qt, rarely rounded limestone clasts deform S0. Limestone fragments (concretions?) may have outer halo of fine grained pyrite. Deformation is weak, we don't see the characteristic contorted 'wormy' bands of typical usms. Deformation increases slightly near the bottom of the USMS interval, fracture spacing decreases, cal-qt infilling fractures is more common and may or may not be associated with pyrite. Pyrite nodules ~1cm in diameter often have halos of calcite with minor qt. The lower contact of usms with actm											

Selwyn Project Diamond Drill Log

Hole Number:
XYC-226

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		is consistent with regional stratigraphy; however, there is a fault gouge zone ~7cm thick that marks the contact. Difficult to speculate on the amount of motion in this zone, if any. » < @ 79.70 Calcite- qt brecciated pyrite. > < @ 80.90 Mudstone/limestone sharp contact at upper interval of faulted ground. > « 80.90- 82.00 Abundantly fractured, mechanically broken, abundant pseudotachylite through fault with weakly to moderately developed slick-n-lines. FLT »« Flt gg 10%»« Flt bx 40%»« Brco 50%» < @ 85.00 Good example of qt-cal veinlet swarms in silicious mudstone. > < @ 91.40 Good example of pseudotachylite and calcic laminae. >									
97.10	124.20	ACTM	634003	97.10	97.50	0.40	2.04	7.23	3.00	280.00	0.28
		ACTM – Active Member	634004	97.50	98.40	0.90	0.74	3.50	2.00	100.00	0.21
			634005	98.40	98.70	0.30	2.05	6.20	3.00	180.00	0.33
		The ACTM consists of a repetitive, possibly rhythmic, sequence of intercalated carbonaceous mudstone, cherty mudstone, chert and limestone and locally contains economically significant Zn and Pb sulphides (see bold marked facies), mainly in its sections with well developed lamination. Because of its heterogeneity, the member is distinctive and easily identified.	634006	98.70	99.30	0.60	0.95	10.92	3.00	280.00	0.09
			634007	99.30	99.80	0.50	1.60	3.00	1.00	90.00	0.53
			634008	99.80	100.80	1.00	0.08	0.53	1.00	10.00	0.15
			634009	100.80	101.70	0.90	0.21	1.39	1.00	40.00	0.15
			634010	101.70	103.30	1.60	0.03	0.10	1.00	5.00	0.30
			634011	101.70	103.30	1.60	0.03	0.10	1.00	5.00	0.30
		=====	634012	103.30	103.80	0.50	1.73	8.19	3.00	260.00	0.21
		The ACTM has 8 different facies:	634013	103.80	104.20	0.40	5.19	19.14	4.00	750.00	0.27
		=====	634014	104.20	105.00	0.80	0.79	0.47	1.00	20.00	1.68
			634015	105.00	105.40	0.40	1.00	1.86	1.00	50.00	0.54
		- GREY CHERT FACIES: Consists of laminated medium light grey to medium dark grey chert. Mineralization: 95-99% quartz and up to 5% secondary calcite.	634016	105.40	105.70	0.30	0.75	2.84	1.00	80.00	0.26
			634017	105.70	106.50	0.80	0.68	2.46	1.00	70.00	0.28
			634018	106.50	106.80	0.30	0.96	4.39	1.00	120.00	0.22
		- WHITISH GREY ZN-PB MUDSTONE FACIES: Is a laminated cherty rock containing up to 70% sulphides. Mineralization: quartz, sphalerite and galena are the major minerals with only minor amounts of pyrite and locally calcite. Sedimentary diagenetic structures are common and well displayed in the facies, such as:	634019	106.80	107.20	0.40	1.14	3.13	1.00	90.00	0.36
			634020	107.20	107.20	0.00	0.01	0.01	1.00	5.00	2.00
			634021	107.20	107.80	0.60	0.89	4.37	1.00	120.00	0.20
			634022	107.80	108.30	0.50	1.31	5.52	3.00	190.00	0.24

Selwyn Project Diamond Drill Log

Hole Number:
XYC-226

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
lamination, pseudo-beds, calcite nodules & limestone nodules and abundant water escape structures. Most obvious structure in facies is cross-cutting veins containing massive sphalerite and galena with minor pyrite. They range in width from 0.5 to 10mm. - THIN BEDDED CHERTY MUDSTONE FACIES: Consists of rhythmic intercalated laminae of chert, carbonaceous mudstone and minor micrite. This facies contains significant amounts of Zn and Pb sulphides. - CHERTY MUDSTONE FACIES: Consists of a greyish black monotonous siliceous, carbonaceous mudstone. It is most typically found overlying the thin bedded calcareous mudstone facies. - THIN BEDDED CALCAREOUS MUDSTONE FACIES: Consists of laminated carbonaceous mudstone containing 20-40% calcite, 40-55% quartz and 10-20% muscovite. Sulphides occur in laminae. In the XY area it is usually the lowest facies in the section to contain laminated sulphides. - CALCAREOUS MUDSTONE FACIES: Consists of grey to greyish black monotonous, calcareous siliceous carbonaceous mudstone. There are no feathery calcite beds or pyrite-calcite blebs in the facies, making it easily distinguishable from the CCMS. - GRADED LIMESTONE FACIES: Is a laminated argillaceous limestone with intercalated carbonaceous limestone laminae. The main rock type in the facies is laminated limestone with laminae up to 0.1-7mm thick. - LIGHT GREY BASAL LIMESTONE FACIES - LGLS: Consists of laminated argillaceous limestone. In the Anniv area it marks the end of the ACTM. It's not always present in the stratigraphy. - BASAL FACIES: This is a highly contorted and locally foliated carbonaceous mudstone. Unlike the other facies it is not repeated higher in the member. It			634023	108.30	108.80	0.50	1.32	1.69	2.00	50.00	0.78
			634024	108.80	109.60	0.80	4.24	1.63	3.00	40.00	2.60
			634025	109.60	110.30	0.70	6.10	33.09	6.00	970.00	0.18
			634026	110.30	110.80	0.50	8.98	26.53	6.00	850.00	0.34
			634027	110.80	111.40	0.60	6.60	23.65	6.00	700.00	0.28
			634028	111.40	111.70	0.30	2.66	6.59	5.00	190.00	0.40
			634029	111.70	112.80	1.10	0.99	4.50	1.00	130.00	0.22
			634030	112.80	112.80	0.00	5.82	6.91	68.00	190.00	0.84
			634031	112.80	113.30	0.50	0.44	5.18	1.00	140.00	0.08
			634032	113.30	113.70	0.40	0.46	8.06	1.00	220.00	0.06
			634033	113.70	114.90	1.20	0.69	0.37	1.00	20.00	1.86
			634034	114.90	115.90	1.00	0.02	0.07	1.00	5.00	0.29
			634035	115.90	116.70	0.80	0.01	0.07	1.00	5.00	0.14
			634036	116.70	117.20	0.50	0.01	0.01	1.00	5.00	2.00
			634037	117.20	117.70	0.50	0.10	0.01	1.00	5.00	20.00
			634038	117.70	118.30	0.60	0.01	0.01	1.00	5.00	2.00
			634039	118.30	119.00	0.70	0.11	0.01	1.00	5.00	22.00
			634040	119.00	119.50	0.50	0.01	0.01	1.00	5.00	2.00
			634041	119.00	119.50	0.50	0.01	0.01	1.00	5.00	2.00
			634042	119.50	119.90	0.40	1.16	0.01	3.00	5.00	232.0
			634043	119.90	120.50	0.60	0.09	0.01	1.00	5.00	18.00
			634044	120.50	121.00	0.50	0.04	0.02	1.00	5.00	2.00
			634045	121.00	121.30	0.30	0.07	0.67	1.00	20.00	0.10
			634046	121.30	122.10	0.80	0.65	0.83	3.00	30.00	0.78
			634047	122.10	123.10	1.00	0.04	0.01	1.00	5.00	8.00
			634048	123.10	123.70	0.60	0.04	0.07	1.00	5.00	0.57
			634049	123.70	124.20	0.50	0.19	1.29	2.00	80.00	0.15

Selwyn Project Diamond Drill Log

Hole Number:
XYC-226

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		appears locally to contain the slip zone of a major slump. The facies has only been observed in the YX area. It is 0.1-2m thick. The facies consists of massive carbonaceous siliceous mudstone with lenses and laminae of contorted, slightly carbonaceous chert. « 97.10- 99.30 Wavy and planar laminated metalliferous, silicious mudstone. Laminae are medium to dark grey, some with brownish colour, typically 1-4mm thick. Minor intervals of massive pyrite occur typically at depositional boundaries with recrystallized qt and calcite. Limestone fragments are sub-angular to rounded, are more abundant lower in interval, typically 1->10cm in diameter. Base metal mineralization consists of mostly fine-grained sphalerite-enriched laminae (~8%) and minor interstitial fine-grained galena (<1.5%). » « 99.30- 103.30 Laminated silicious mudstone. No visible base metal mineralization, only inferred sphalerite-enrichments in some lamina, up to 0.5%. Conformable qt-cal remineralizes between laminae ~3-7mm thick. Blocky ground-abundant machine breaks. Rock interval here is more similar to usms lithology. Some fracture faces have weakly developed slick-n-lines. » « 99.30- 103.00 FLT »« Flt gg 10%»« Flt bx 30%»« Brco 60%» « 103.30- 103.80 Strongly pyritic laminated metaliferous mudstone. Base metal mineralization consists of about 9.7% Zn and 2.3% Pb, both from very fine grained sphalerite and galena laminae. Limestone fragments occur in this interval, they are light grey and laminated, typically subrounded, 3-10cm diameter. » « 103.80- 104.20 Mingled light grey limestone, calcareous mudstone and silicious mudstone. Remobilized wispy stringers of galena, sphalerite laminae (broken up typically). Zn ~14%, Pb~12%. Clastic texture throughout interval, mostly sub-angular to sub-rounded clasts. » « 104.20- 105.00 Weakly to moderately laminated limestone, discontinuous qt-cal veinlets are discordant to S0. Framboidal py 1-8mm diameter is common									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-226

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		throughout. Only weak base metal mineralization (Pb + Zn ~1%), through fractures, mud, as well as cal-qt infills. » « 105.00- 105.40 Laminated calcareous mudstone with limestone fragments near base. » « 105.40- 106.80 Laminated siliceous and weakly calcareous mudstone as described, very little visible mineralization. More sphalerite than galena (Zn>Pb)~2%. Rare blebs of coarse grained galena (trace amount). » « 106.80- 108.30 Laminated muddy limestone, sphalerite enrichments in some laminae. Rounded to sub-rounded limestone clasts 2-10cm in diameter are pervasive throughout . Galena mineralization is patchy and typically occurs as stringers and blebs with calcite and qt. Pb~1.75%, Zn~2-5%, corresponding with mud-rich zones. The limestone itself is not mineralized much, but the mud inter-laminated with it is.» « 108.30- 109.60 Laminated mudstone as described, some 4-15cm metalliferous sections with up to 3% Zn and 3% Pb. Galena tends to be coarser grained and form <1mm thick stringers and occasionally blows out into blebs. Broken up limestone laminae and laminated limestone clasts are typical of this interval. » « 109.60- 111.40 High-grade interval of laminated brownish grey metalliferous mudstone. Laminae are often faulted and have seen mobilization of qt-sph-mud down-hole along fractures. This causes a discordant style of « sph » Quartz fragments are common in some sections (typ 1-10mm long). It appears as though a sph-rich brine has migrated downwards roughly orthogonal to S0, often causing soft-sediment deformation. Sphalerite may also form blebs of slightly coarser grains, this could be a later-stage mineralization event. » « 111.40- 111.70 Massive to semi-massive pyrite, intercalated with base metal-mineralized muddy laminae, limestone clasts and cherty laminae. Pb ~7%, Zn ~ 15%. »									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-226

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		« 111.70- 125.80 Fairly low grade section of ACTM with patchy zones <50cm thick with up to 7% Zn. The interval consists of intercalated calcareous, silicious mudstone and laminated muddy limestone which is mostly barren to base metals. Samples have been largely broken up based on calcareous content, except where mineralization is apparent- then that takes priority. The mudstone has laminae 2-6mm thick, typically planar with variable amounts of disseminated pyrite. »									
124.20	125.80	CCMS	634050	124.20	124.20	0.00	0.01	0.01	1.00	5.00	2.00
		CCMS – Calcareous Mudstone Massive, calcareous, carbonaceous, dark grey mudstone. Most of the member is massive, but rare poorly defined bedding and pyrite-calcite micro-concretions are present. Most diagnostic structures are feathery calcite beds (=thin calcite-cemented concretions, many of them contain pyrite cores) and calcite pseudo-beds (= fibrous calcite vein parallel to bedding). « lm ca 5.00-10.00mm », « nodules py -3.00% 2.00-20.00mm » « 124.2- 125.8 FLT »« Flt gg 10%»« Flt bx 65%»« Brco 25%»									
125.80	125.80	EOH									

Diamond Drill Log

Comprehensive Report for Hole:

XYC-225

Hole No.: XYC-225	Depth: 654.40 m	Horizontal Length: 0.00 m	Project: 1710
Location Data:			
Property:	Selwyn Project	Claim Name:	X46
Mining District:	Selwyn Basin	Grant Number:	Y 64679
Province/Territory:	Yukon		
UTM Co-Ordinates & Altitude of Drill Hole Collar:			
UTM Easting:	487502.64 m	True Azimuth:	38.5 °
UTM Northing:	6927240.25 m	Hole Angle:	-65.0 °
Elevation (m):	1486.18 m	NTS Name:	Placer Creek
		NTS Number:	105I06
Grid Co-Ordinates of Drill Hole Collar:			
Grid Easting (m):	0.00 m	Grid Name:	HP 06
Grid Northing (m):	0.00 m	Grid Type:	100m
Grid Azimuth:	98.5 °		
Dimond Drilling Contract:			
Drilled By:	NL-02	Date Drilling Start:	10/8/2010
		Date Finish:	10/23/2010
Diamond Drill Core:			
Logged By:	Kate Cameron/ Helena	Date Logging Start:	10/25/2010
		Date Finish:	10/29/2010
Legend for Core Logging Codes: PAX			
Core Size:	NQ/BQ	Cemented:	Yes
Casing Depth:	8.10 m	Casing Pulled:	
Water Depth:	0.00 m	Overburden Depth:	8.10 m
Level:	Section:	Drift:	

Selwyn Project

Diamond Drill Log

Survey Data for Hole

XYC-225

Hole Comments:

Fri, Oct 08 --- Rods are stuck in XYC 220 (target #48), unable to recover. The NQ string is to be left in the hole with the casing capped. Drill to adjust for target #47 and attempt to intersect second ACTM lens. If this hole hits the second ACTM lens we will return to the previous hole and reduce to BQ, if it doesn't hit the second lens we'll go back to the previous hole and cut the rods.

=====

Sat, Oct 09 --- At a total depth of 98.6m. Hole was collared into FLMD. Fault gouge, blocky ground and poor recovery between 92.6- 98.6m.

=====

Sun, Oct 10 --- At a total depth of 140m. Still in FLMD, out of blocky ground.

=====

Mon, Oct 11 --- Still at a total depth of 140m in FLMD. Core barrel jammed with cuttings in it. They had to pull rods and try again.

=====

Tue, Oct 12 --- At a total depth of 183m in FLMD. No core received from last night's shift.

=====

Wed, Oct 13 --- At a total depth of 209.6m in FLMD. Drill has been stuck all night, hole caved in. They hit a small aquifer at 160m and a larger one at 185m, they are still dealing with the water from that one. We will try to reduce to BQ and continue with today's shift.

=====

Thu, Oct 14 --- Still at a total depth of 209.6m. Troubles with hole producing water. Nightshift set up BQ rods to hopefully continue drilling today.

=====

Fri, Oct 15 --- Drilling with BQ over the past two shifts to a current depth of 273.4 meters. In competent FLMD.

=====

Sat, Oct 16 --- Still drilling in FLMD at 346.6 meters, although we may see the FLMD-USMS contact in the last meter of core that has been brought down. Core is competent; no significant drilling problems at this time. No recent flexit tests because we are having problems finding flexit parts for the BQ rods.

=====

Sun, Oct 17 --- Drilling through competent USMS with BQ at 398 meters. No mechanical problems to report. Adam and Keith have helped to repair a small problem with the flexit that is able to work with BQ rods, so that it now fits through the BQ bit and is working properly. The FLMD-USMS contact was at approximately 346 meters.

=====

Mon, Oct 18 --- Drilling through competent USMS with BQ at 471.5 meters. No problems to report.

=====

Tue, Oct 19 --- Hit Active Member at 475.5 meters, and are still in Active Member at 529.1 meters. From 476.7 to 478.5 meters we have high grade material of at least 25% combined. Drilling is going well.

=====

Wed, Oct 20 --- Drilled through low to medium grade ACTM to 558 meters, where we hit a fairly unimpressive 1.5 meter fault, and promptly transitioned to Flaggy Mudstone. Now at 575 meters, fairly competent but slow

Selwyn Project

Diamond Drill Log

Survey Data for Hole

XYC-225

drilling.

=====

Thu, Oct 21 --- Slow drilling at 605.6 meters in competent rock. The core continues to show sporadic short ranges of light grey siliceous bioturbated rock (FLMD-like), but is primarily weakly laminated medium-dark grey siliceous mudstone with some faint bioturbations. Bedding-parallel elongate pyrite nodules are also visible. I am confident that we are either in a primarily carbonaceous range of FLMD, or the lower part of BSSM. Dip of hole at bottom is now only 36 degrees. We will continue drilling; another strange hole.

=====

Fri, Oct 22 --- Slow drilling at 627.6 meters in generally competent rock. Core is weakly medium grey siliceous mudstone with sporadic, faint bioturbations and weakly laminated locally. Contains some concretions, a very low abundance of veins, and continues to show faint elongate pyrite nodules. The unit is almost certainly BSSM, and given the abundance of bioturbations is decreasing, strongly suspect drilling upwards in stratigraphy.

=====

Sat, Oct 23 --- Shut down XYC-225 in BSSM last night at approximately 654 meters. Pulled ~450 meters of BQ rods and cemented by pumping 700 feet of cement through the NQ rods, as the hole was making water. This was successful, but the NQ rods could not be extracted last night. The NQ rods are loose, however, and are now below the core barrel. They will try to extract the rod string with a swedge today, and failing that, will cut the core barrel off and extract rods that way. If successful, we will turn the drill today and commence drilling XYC-237, new target #62, on same pad. Some flexit tests were missed and could not easily be done last night during what was a very difficult shift of cementing and pulling rods.

<i>Depth</i>	<i>Dip</i>	<i>Azimuth</i>
0.00	-65.0	38.5
50.00	-63.0	36.5
107.00	-63.0	34.6
200.00	-60.3	29.9
374.00	-52.5	34.7
419.70	-50.1	39.5
459.30	-47.8	40.5
505.10	-44.2	39.7
602.60	-35.9	37.7
627.00	-35.5	41.7

Selwyn Project Diamond Drill Log

Hole Number:
XYC-225

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
0.00	8.10	OVBR									
8.10	343.80	FLMD									
<i>FLMD – Flaggy Mudstone Formation</i> <i>Dark grey mudstone in the upper portions of the unit grading into light grey mudstone to siltstone. Contains abundant wispy bioturbation which ranges from randomly-oriented at the top of the unit to bedding-parallel throughout the majority of the unit. Darker upper section has a strong fetid odour along broken surfaces. « btrb 0.10-2.00cm », « cg xtl crns ca 1.00-5.00% 5.00-150.00cm », « crns py 1.00-5.00% 0.10-0.50mm »,</i> <i>« 8.10- 41.60 Broken zone. FLT »« Flt gg 5%»« Flt bx 5%»« Brco 40%»</i> <i>< @ 29.10 S0 in bioturbations parallel tca. S0 tca 0° ></i> <i>< @ 38.80 S0 in bioturbations. S0 tca 20° ></i> <i>< @ 44.70 S0 in bioturbations. S0 tca 20° ></i> <i>< @ 52.40 S0 in bioturbations. S0 tca 20° ></i> <i>< @ 67.10 S0 in bioturbations. S0 tca 30° ></i> <i>< @ 77.50 S0 in bioturbations. S0 tca 35° ></i> <i>< @ 90.60 S0 in bioturbations. S0 tca 45° ></i> <i>« 92.90- 134.60 Fault. Black gouge dominates. Some calcite vein remnants and small runs of FLMD. Zones in middle and at end are just broken. FLT »« brco 5%»« bx 10%»« gg 60%»</i> <i>« 197.10- 200.60 Fault. Some core loss. FLT »« brco 10%»« bx 25%»« gg 5%»</i>											

Selwyn Project Diamond Drill Log

Hole Number:
XYC-225

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		« 202.80- 208.30 Fault. Core is well broken in this zone. FLT »« brco 25%»« bx 25%» < @ 215.50 Bedding in lamination and calcite veins S0 TCA 55° > < @ 323.00 Bedding in darker banding within a zone of very weak bioturbation. S0 TCA 50° > « 329.00- 343.80 Dark stretch of flaggy mudstone. »									
343.80	475.40	USMS	633451	350.50	352.70	2.20					
		USMS – Upper Siliceous Mudstone	633452	352.70	353.30	0.60					
		Consists of interlaminated dark grey to black mudstone and light to medium grey chert. Regionally, a 1m thick graptolite zone occurs 15m below the top of the upper unit, this is usable as a horizon. The USMS is divided into 3 units. The Lower Unit contains abundant limestone concretions and Galena and sphalerite micro-concretions occur locally near the base of this unit. « gra , lm chrt -20.00% », « cg xtl sph crns ca 5.00-20.00cm », « bed chrt 10.00-15.00% », « 344.40- 343.80 Fault FLT » « Weakly mineralized zone; not visible, but Niton reads 4.47% Zn and 0.15 Pb. » < @ 355.70 Bedding in cherty bands. S0 TCA 40° > « 358.50- 360.10 Great mineralization. Sphalerite in laminae. Traces of galena in bleby veins. Niton: 17.3% Zn and 2.0% Pb. » < @ 358.00 Bedding in sphalerite laminae S0 TCA 15-25° >	633453	353.30	355.70	2.40					
			633454	355.70	356.60	0.90					
			633455	356.60	358.70	2.10					
			633456	358.70	360.10	1.40					
			633457	360.10	361.40	1.30					
			633458	361.40	362.80	1.40					
			633459	472.20	473.90	1.70					
			633460	473.90	475.40	1.50					
			633461	473.90	475.40	1.50					

Selwyn Project Diamond Drill Log

Hole Number:
XYC-225

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		« 360.10- 372.00 Weakly mineralized zone. Nothing visible. Niton: <0.1% Zn and <0.1% Pb. » < @ 365.80 Bedding in chert bands. S0 TCA 30° > < @ 371.40 Bedding in chert bands. S0 TCA 20° > < @ 377.40 Bedding in chert bands. S0 TCA 40° > < @ 386.00 Bedding in chert bands. S0 TCA 30° > Below this is it difficult to get representative bedding angles with confidence due to variability of chert bands and not much pyritic laminae. Lots of limestone clasts. Many are recrystallized graded limestone (~5 - 80 cm diameter). Limestone proportion seems to increase down section (~30-40%). Calcite veining predominates with some quartz veins present as well. Qtz-calc stylolites common. < @ 427.60 Bedding defined by pyrite laminae S0 TCA 49° >									
475.40	537.50	ACTM	633462	475.40	476.10	0.70					
		ACTM – Active Member	633463	476.10	476.50	0.40					
			633464	476.50	477.60	1.10					
		The ACTM consists of a repetitive, possibly rhythmic, sequence of intercalated carbonaceous mudstone, cherty mudstone, chert and limestone and locally contains economically significant Zn and Pb sulphides (see bold marked facies), mainly in its sections with well developed lamination. Because of its heterogeneity, the member is distinctive and easily identified.	633465	477.60	478.10	0.50					
			633466	478.10	478.30	0.20					
			633467	478.30	478.80	0.50					
			633468	478.80	478.90	0.10					
			633469	478.90	480.10	1.20					
			633470	480.10	480.10	0.00					
		=====	633471	480.10	481.00	0.90					
		The ACTM has 8 different facies:	633472	481.00	481.70	0.70					
		=====	633473	481.70	482.60	0.90					
			633474	482.60	483.10	0.50					

Selwyn Project Diamond Drill Log

Hole Number:
XYC-225

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
- GREY CHERT FACIES: Consists of laminated medium light grey to medium dark grey chert. Mineralization: 95-99% quartz and up to 5% secondary calcite.			633475	483.10	483.50	0.40					
			633476	483.50	486.20	2.70					
			633477	486.20	487.30	1.10					
			633478	487.30	488.10	0.80					
- WHITISH GREY ZN-PB MUDSTONE FACIES: Is a laminated cherty rock containing up to 70% sulphides. Mineralization: quartz, sphalerite and galena are the major minerals with only minor amounts of pyrite and locally calcite. Sedimentary diagenetic structures are common and well displayed in the facies, such as: lamination, pseudo-beds, calcite nodules & limestone nodules and abundant water escape structures. Most obvious structure in facies is cross-cutting veins containing massive sphalerite and galena with minor pyrite. They range in width from 0.5 to 10mm.											
			633479	488.10	488.60	0.50					
			633480	488.60	488.60	0.00					
			633481	488.60	489.80	1.20					
			633482	489.80	490.60	0.80					
			633483	490.60	491.00	0.40					
			633484	491.00	492.90	1.90					
			633485	492.90	493.90	1.00					
			633486	493.90	494.80	0.90					
			633487	494.80	495.60	0.80					
- THIN BEDDED CHERTY MUDSTONE FACIES: Consists of rhythmic intercalated laminae of chert, carbonaceous mudstone and minor micrite. This facies contains significant amounts of Zn and Pb sulphides.			633488	495.60	496.00	0.40					
			633489	496.00	496.40	0.40					
			633490	496.40	496.90	0.50					
			633491	496.40	496.90	0.50					
- CHERTY MUDSTONE FACIES: Consists of a greyish black monotonous siliceous, carbonaceous mudstone. It is most typically found overlying the thin bedded calcareous mudstone facies.			633492	496.90	498.30	1.40					
			633493	498.30	499.20	0.90					
			633494	499.20	500.50	1.30					
			633495	500.50	501.70	1.20					
- THIN BEDDED CALCAREOUS MUDSTONE FACIES: Consists of laminated carbonaceous mudstone containing 20-40% calcite, 40-55% quartz and 10-20% muscovite. Sulphides occur in laminae. In the XY area it is usually the lowest facies in the section to contain laminated sulphides.											
			633496	501.70	503.20	1.50					
			633497	503.20	503.30	0.10					
			633498	503.30	504.10	0.80					
- CALCAREOUS MUDSTONE FACIES: Consists of grey to greyish black monotonous, calcareous siliceous carbonaceous mudstone. There are no feathery calcite beds or pyrite-calcite blebs in the facies, making it easily distinguishable from the CCMS.			633499	504.10	504.60	0.50					
			633500	504.60	504.60	0.00					
			636401	504.60	505.80	1.20					
			636402	505.80	506.40	0.60					
- GRADED LIMESTONE FACIES: Is a laminated argillaceous limestone with intercalated carbonaceous limestone laminae. The main rock type in the facies is laminated limestone with laminae up to 0.1-7mm thick.			636403	506.40	508.10	1.70					
			636404	508.10	509.10	1.00					
			636405	509.10	509.70	0.60					
			636406	509.70	510.40	0.70					
			636407	510.40	510.50	0.10					

Selwyn Project Diamond Drill Log

Hole Number:
XYC-225

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
- <i>LIGHT GREY BASAL LIMESTONE FACIES - LGLS: Consists of laminated argillaceous limestone. In the Anniv area it marks the end of the ACTM. It's not always present in the stratigraphy.</i> - <i>BASAL FACIES: This is a highly contorted and locally foliated carbonaceous mudstone. Unlike the other facies it is not repeated higher in the member. It appears locally to contain the slip zone of a major slump. The facies has only been observed in the YX area. It is 0.1-2m thick. The facies consists of massive carbonaceous siliceous mudstone with lenses and laminae of contorted, slightly carbonaceous chert.</i> « 475.40- 537.50 Contact with USMS marked by appearance of fine laminae and mineralization. Some rare galena vein in USMS above contact however. » « 475.40- 476.10 Medium to dark grey laminated silicious mudstone. Fine-grained galena veins and possibly sphalerite laminae. » « 476.10- 476.50 Light to medium grey weakly calcareous mudstone. Laminated. Coarse grained sphalerite with calcite. Limestone clast ~4 cm wide present. » « 476.50- 477.60 Light yellow-grey moderately calcareous mudstone. High grade mineralization. Laminae are folded. Parallel fine-grained galena veins (~1mm thick) on laminae axial cleavages, very regular (c-s fabric). Sphalerite is generally fine grained in laminae. Looks similar to 'feeder zone' Active Member of DON-157. » « 477.60- 480.10 Medium to dark grey laminated silicious mudstone. Laminae are mostly 'mangled' and distorted. Lots of pyrite (laminae?) and calcite veins. Coarse-grained galena + calcite veins, as well as fine grained galena veins following cleavages. Sphalerite is very fine grained. » « 478.90- 480.00 FLT »« Flt gg 5%»« Flt bx 65%»« Brco 30%»			636408	510.50	511.00	0.50					
			636409	511.00	511.40	0.40					
			636410	511.40	511.40	0.00					
			636411	511.40	512.30	0.90					
			636412	512.30	513.20	0.90					
			636413	513.20	514.10	0.90					
			636414	514.10	515.30	1.20					
			636415	515.30	516.10	0.80					
			636416	516.10	517.20	1.10					
			636417	517.20	518.70	1.50					
			636418	518.70	519.00	0.30					
			636419	519.00	519.30	0.30					
			636420	519.30	520.00	0.70					
			636421	519.30	520.00	0.70					
			636422	520.00	520.50	0.50					
			636423	520.50	520.80	0.30					
			636424	520.80	521.50	0.70					
			636425	521.50	521.80	0.30					
			636426	521.80	521.90	0.10					
			636427	521.90	523.60	1.70					
			636428	523.60	524.10	0.50					
			636429	524.10	524.90	0.80					
			636430	524.90	524.90	0.00					
			636431	524.90	525.80	0.90					
			636432	525.80	526.50	0.70					
			636433	526.50	527.20	0.70					
			636434	527.20	528.10	0.90					
			636435	528.10	528.60	0.50					
			636436	528.60	529.00	0.40					
			636437	529.00	529.40	0.40					
			636438	529.40	530.90	1.50					
			636439	530.90	532.20	1.30					
			636440	532.20	532.20	0.00					
			636441	532.20	533.40	1.20					

Selwyn Project Diamond Drill Log

Hole Number:
XYC-225

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		« 480.10- 481.00 Light-grey medium to coarse grained graded limestone. No mineralization visible. »	636442	533.40	534.30	0.90					
			636443	534.30	534.80	0.50					
			636444	534.80	535.50	0.70					
			636445	535.50	536.40	0.90					
		« 481.00- 483.10 Medium to dark grey silicious mudstone. Laminations are often block faulted. Calcite stylolites common. Pyrite and calcite +/- galena blebs/veins occur as well. »	636446	536.40	537.50	1.10					
		« 483.10- 488.10 Dark-grey interlayered calcareous and silicious mudstone. Layers are too small to pull out separately. Laminae are generally planar with some faulted/ distorted sections. »									
		« 488.10- 488.60 Medium-grey muddy limestone. Parallel, planar calcite veins as well as 'whisps' very common. Not a clast. »									
		« 488.60- 494.80 Dark-grey silicious mudstone. A few limestone clasts, laminae are faint to absent. Galena and sphalerite present in veins, galena with calcite + pyrite as well in areas. Calcite stylolites present.»									
		« 494.80- 495.60 Light-grey and dark brownish grey mangled laminated silicious mudstone and graded limestone. Laminae are very distorted. Sphalerite laminae visible. Quite a bit of pyrite in mudstone as well as pyrite and calcite veins. »									
		« 495.60- 496.00 Medium to dark-grey recrystallized graded limestone with ~50% silicious laminated mudstone. Laminae are planar for the most part. Galena coarse-grained vein visible. »									
		« 496.00- 496.40 Light-grey recrystallized graded limestone. Not sure if its a clast or not. »									
		« 496.40- 496.90 Medium to dark grey, laminated weakly calcareous mudstone with limestone clasts 0.5-2cm diameter. Laminae is faulted and offset. Mud +/- galena fill fault planes. Some coarse grained sphalerite and galena. Pyrite is also present. »									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-225

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		« 496.90- 499.20 Light grey limestone with mud laminae interspersed throughout. Pyrite + calcite veining, as well as calcite + breccia mud veins. »									
		« 499.20- 500.50 Medium-grey laminated silicious mudstone. Laminae are heavily faulted (faults filled with mud/fine grained sulfides). Coarse grained galena blebs pres ent. »									
		« 500.50- 501.70 Light grey limestone with occasional mud laminae. »									
		« 501.70- 503.20 Medium-grey laminated silicious mudstone. Laminae are heavily faulted and offset by microfaults. »									
		« 503.20- 503.30 Medium-grey laminated calcareous mudstone. Sphalerite laminae possible. »									
		« 503.30- 504.10 Light-medium grained calcareous mudstone greater than limestone. »									
		« 504.60- 506.40 Medium to dark grey calcareous laminated mudstone. Calcite laminae common. Fine grained sulphide mineralization. »									
		« 506.40- 509.70 Medium to dark grey laminated silicious mudstone with sections of limestone (clasts?) and/ or calcareous mudstone. Laminae are distorted by faulting. Coarse grained galena blebs and stringers and fine grained sphalerite laminae seen. »									
		« 509.70- 510.40 Medium to light grey muddy limestone (calcareous mudstone?). Coarse grained galena bleb seen. »									
		« 510.40- 510.50 Dark grey laminated silicious mudstone, with distorted laminae. »									
		« 510.50- 511.00 Light grey graded limestone. No mineralization visible.									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-225

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
»											
« 511.00- 511.40 Black unlaminated silicious mudstone. »											
« 511.40- 512.30 Light grey (has a yellow post-drilling stain) calcareous mudstone. »											
« 512.30- 514.10 Light grey graded limestone with mud laminae. »											
« 514.10- 515.30 Medium to light grey calcareous mudstone and limestone. »											
« 515.30- 517.20 Light grey limestone. Calcite and mud stylolites seen. »											
« 517.20- 519.00 Light to medium grey calcareous mudstone. Mud and calcite stylolites seen. »											
« 519.00- 519.30 Light grey limestone. »											
« 519.30- 520.00 Medium grey calcareous mudstone (possibly limestone?). Lots of disseminated calcite. »											
« 520.00- 520.50 Light to medium grey metalliferous calcareous mudstone. Galena and sphalerite mineralization visible (both fine and coarse grained galena). High grade. »											
« 520.50- 520.80 Dark grey calcareous mudstone with calcite veining ~3mm thick. »											
« 520.80- 521.50 Dark to medium grey laminated silicious mudstone. Laminae are distorted. No mineralization visible. Calcite veining throughout. »											
« 521.50- 521.80 Light to medium grey metalliferous mudstone. Laminated.											

Selwyn Project Diamond Drill Log

Hole Number:
XYC-225

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		Very high grade. Galena and sphalerite as veins/laminations. » « 521.80- 521.90 Light to medium-grey calcareous mudstone. Fractured. » « 521.90- 523.60 Medium to dark grey laminated silicious mudstone. Laminae are generally planar. Coarse grained sphalerite with calcite in veins, coarse and fine grained galena. » « 523.60- 524.10 Light to medium grey calcareous mudstone. Laminae are faulted in places. Calcite + mud stylolites. » « 524.10- 525.80 Light grey graded to massive limestone. Calcite + mud stylolites common. No mineralization visible. » « 525.80- 526.50 Medium grey laminated silicious mudstone. Kinda carbonaceous. Laminae are faulted. » « 526.50- 527.20 Light grey limestone with a lot of calcite veining. » « 527.20- 528.10 Black silicious mudstone with layers / clasts of light grey limestone up to 8cm wide. » « 528.10- 528.60 Light to medium grey laminated silicious mudstone, metalliferous. High grade, similar to previous high grade intervals. » « 528.60- 529.00 Laminated medium grey silicious mudstone. » « 529.00- 529.40 Medium to light grey laminated metalliferous silicious mudstone. Laminae are faulted and filled with galena +/- sphalerite. » « 529.40- 533.40 Light to medium grey laminated in places calcareous mudstone. Lots of calcite and mud stylolites and stringers and veins. No mineralization visible. »									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-225

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
« 533.40- 534.30 Light grey limestone. »											
« 534.30- 534.80 Medium to dark grey moderately calcareous mudstone. Calcite stylolites frequent. No mineralization visible. »											
« 534.80- 536.40 Dark grey to black, laminated in places, silicious mudstone. Calcite veins and stylolites common. »											
« 536.40- 537.50 Light grey muddy limestone, calcite whisps common. No mineralization visible. Possibly basal limestone. Contact with CCMS is gradational. »											
537.50	538.80	CCMS									
CCMS – Calcareous Mudstone			636447	537.50	539.30	1.80					
Massive, calcareous, carbonaceous, dark grey mudstone. Most of the member is massive, but rare poorly defined bedding and pyrite-calcite micro-concretions are present. Most diagnostic structures are feathery calcite beds (=thin calcite-cemented concretions, many of them contain pyrite cores) and calcite pseudo-beds (= fibrous calcite vein parallel to bedding).											
« lm ca 5.00-10.00mm », « nodules py -3.00% 2.00-20.00mm »,											
538.80	555.80	FLT	636448	539.30	540.80	1.50					
« 538.80- 555.80 Fairly carbonaceous fault zone. Rock is very fractured but there is not that much gouge or breccia (possibly washed away?). FLT »« Flt gg 5%»« Flt bx 15%»« Brco 70%»			636449	546.40	548.10	1.70					
« 538.8- 550.0 CCMS »			636450	548.10	550.00	1.90					
« 550.00- 550.80 Weakly calcareous, laminated mudstone. ACTM »			636451	548.10	550.00	1.90					
« 550.80- 551.40 Silicious laminated mudstone. ACTM »			636452	550.00	550.80	0.80					
			636453	550.80	551.40	0.60					
			636454	551.40	551.70	0.30					
			636455	551.70	552.00	0.30					
			636456	552.00	554.00	2.00					
			636457	554.00	555.60	1.60					

Selwyn Project Diamond Drill Log

Hole Number:
XYC-225

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		« 551.40- 551.70 Limestone. ACTM »									
		« 551.70- 552.00 Silicious, metalliferous, laminated mudstone. High grade. ACTM »									
		« 554.10- 555.80 BSSM »									
555.80	654.40	BSSM									
		BSSM – Backside Siliceous Mudstone									
		Devonian Siliceous Mudstone – Upper Chert Formation									
		Greyish black laminated chert and siliceous mudstone. Randomly-oriented to bedding-parallel bioturbation is common in the bottom of the unit. « lm chrt 75.00-95.00% », « btrb 0.10-2.00cm »,									
		« 555.80- 654.40 Dark grey to black laminated mudstone with some light grey FLMD like sections. Downsection, unit looks very monotonous, almost CCMS-like but with some limestone clasts present. Fine laminations are present, but not as obvious as in Transitional Formation. »									
		« 556.90- 557.10 FLT »« Flt gg 40%»« Flt bx 60%»									
		« @ 569.60 S0 defined by layering colour change. S0 tca 41° »									
		« 599.60- 560.40 FLT »« Flt gg 5%»« Flt bx 95%»									
		« @ 603.90 S0 defined by layering. S0 tca 20° »									
		« @ 622.50 S0 defined by pyrite laminae. S0 tca 25° »									
		« @ 643.90 S0 defined by pyrite laminae. S0 tca 43° »									
654.40	654.40	EOH									

Diamond Drill Log

Comprehensive Report for Hole:

XYC-224

Hole No.: XYC-224	Depth: 213.20 m	Horizontal Length: 0.00 m	Project: 1710
Location Data:			
Property:	Selwyn Project	Claim Name:	X 13
Mining District:	Selwyn Basin	Grant Number:	Y 64538
Province/Territory:	Yukon		
UTM Co-Ordinates & Altitude of Drill Hole Collar:			
UTM Easting:	488938.00 m	True Azimuth:	210.0 °
UTM Northing:	6926346.00 m	Hole Angle:	-65.0 °
Elevation (m):	1647.00 m	NTS Name:	Placer Creek
		UTM Datum:	NAD 83
		UTM Grid Zone:	9
		NTS Number:	105I06
Grid Co-Ordinates of Drill Hole Collar:			
Grid Easting (m):	0.00 m	Grid Name:	HP 06
Grid Northing (m):	0.00 m	Grid Type:	100m
Grid Azimuth:	270.0 °		
Dimond Drilling Contract:			
Drilled By:	CY-01	Date Drilling Start:	10/08/2010
		Date Finish:	10/12/2010
Diamond Drill Core:			
Logged By:	Graham Leroux / Kate	Date Logging Start:	10/30/2010
		Date Finish:	11/09/2010
Legend for Core Logging Codes: PAX			
Core Size:	NQ/NQ3	Cemented:	Yes
Casing Depth:	4.60 m	Casing Pulled:	Yes
Water Depth:	0.00 m	Overburden Depth:	4.60 m
Level:	Section:	Drift:	

Selwyn Project

Diamond Drill Log

Survey Data for Hole

XYC-224

Hole Comments:

Fri, Oct 08 --- Drill moved to target #7 yesterday. 14 feet of casing, at a total depth of 23m in FLMD

=====

Sat, Oct 09 --- total depth of 116m in USMS. Drill is losing hydraulic oil last night, day shift will have to fix the problem and continue drilling.

=====

Sun, Oct 10 --- At a total depth of 143.2m in USMS, using the devicore, they had issues with their hydraulic cooler

=====

Mon, Oct 11 ---Total depth of 204.2m in CCMS. Hit active member from 163.5-195.5m. I am going to let them drill another 15m, maybe be able to shut down by lunch and move today.

=====

Tue, Oct 12 --- Total depth of 212.7m in CCMS, drill shut down at this depth and moved to set up #13.

<i>Depth</i>	<i>Dip</i>	<i>Azimuth</i>
0.00	-65.0	210.0
50.00	-64.7	207.9
101.00	-63.9	209.7
150.20	-63.6	207.7
207.00	-63.4	209.9

Selwyn Project Diamond Drill Log

Hole Number:
XYC-224

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
0.00	4.60	OVBR									
4.60	82.60	FLMD									
<i>FLMD – Flaggy Mudstone Formation</i> <i>Dark grey mudstone in the upper portions of the unit grading into light grey mudstone to siltstone. Contains abundant wispy bioturbation which ranges from randomly-oriented at the top of the unit to bedding-parallel throughout the majority of the unit. Darker upper section has a strong fetid odour along broken surfaces. « btrb 0.10-2.00cm », « cg xtl crns ca 1.00-5.00% 5.00-150.00cm », « crns py 1.00-5.00% 0.10-0.50mm »,</i> <i>< @ 18.20 bioturbated S0, tca 45° ></i> <i>< @ 31.60 bioturbated S0, tca 45° ></i> <i>< @ 43.20 bioturbated S0, tca 35° ></i> <i>< @ 69.00 bioturbated S0, tca 50° ></i>											
82.60	163.50	USMS	633851	120.80	121.80	1.00	0.13	0.16	3.00	5.00	0.81
<i>USMS – Upper Siliceous Mudstone</i> <i>Consists of interlaminated dark grey to black mudstone and light to medium grey chert. Regionally, a 1m thick graptolite zone occurs 15m below the top of the upper unit, this is usable as a horizon. The USMS is divided into 3 units. The Lower Unit contains abundant limestone concretions and Galena and sphalerite micro-concretions occur locally near the base of this unit. « gra , lm chrt -20.00% », « cg xtl sph crns ca 5.00-20.00cm », « bed chrt 10.00-15.00% »,</i> <i>< @ 91.90 cherty bands s0 tca 55° ></i> <i>« 96.00- 97.20 flt »« flt bx 30%»« bkn 70%»</i> <i>< @ 109.30 chert bands s0 tca 70° ></i> <i>« 121.80- 122.60 visible sph in fine laminae, distorted by microfaults;</i>			633852	121.80	122.60	0.80	0.78	5.99	7.00	160.00	0.13
			633853	122.60	123.00	0.40	0.07	0.04	1.00	5.00	1.75
			633854	160.80	161.80	1.00	0.02	0.20	3.00	5.00	0.10
			633855	161.80	162.30	0.50	0.01	0.11	2.00	5.00	0.09
			633856	162.30	163.50	1.20	0.03	0.68	3.00	30.00	0.04

Selwyn Project Diamond Drill Log

Hole Number:
XYC-224

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		visible gal traces; NITON: 0.43% Pb, 8.35% Zn » ‹ @ 131.40 planar parallel chert bands s0 tca 85° › ‹ 136.70- 138.20 flt › ‹ flt gg 100% › ‹ 142.70- 150.20 flt › ‹ bkn 65% › ‹ flt bx 15% › ‹ flt gg 20% › ‹ 150.20- 163.50 Intercalated carb mdst & graded lam'd lmst, typ of lower usms. Thin wispy calc lam's, many cross-cutting cal veins. Mdst banded (cherty and cal). › ‹ @ 163.5 Lower contact of limestone often deforms the mudstone, similar to the way a large clast can load underlying sediment. ›									
163.50	195.50	ACTM	633857	163.50	164.10	0.60	1.61	7.76	3.00	310.00	0.21
		ACTM – Active Member	633858	164.10	164.80	0.70	3.61	18.86	4.00	850.00	0.19
			633859	164.80	165.30	0.50	3.17	16.03	3.00	850.00	0.20
		The ACTM consists of a repetitive, possibly rhythmic, sequence of intercalated carbonaceous mudstone, cherty mudstone, chert and limestone and locally contains economically significant Zn and Pb sulphides (see bold marked facies), mainly in its sections with well developed lamination. Because of its heterogeneity, the member is distinctive and easily identified.	633860	165.30	166.00	0.70	7.04	10.88	5.00	500.00	0.65
			633861	165.30	166.00	0.70	5.55	13.23	5.00	620.00	0.42
			633862	166.00	166.50	0.50	0.47	2.23	3.00	70.00	0.21
			633863	166.50	167.20	0.70	1.11	6.83	3.00	160.00	0.16
			633864	167.20	167.50	0.30	2.45	3.76	4.00	90.00	0.65
			633865	167.50	168.50	1.00	0.02	0.20	1.00	5.00	0.10
		=====	633866	168.50	169.10	0.60	0.08	0.86	1.00	20.00	0.09
		The ACTM has 8 different facies:	633867	169.10	170.20	1.10	0.39	3.17	1.00	90.00	0.12
		=====	633868	170.20	170.90	0.70	0.06	0.51	2.00	10.00	0.12
			633869	170.90	171.20	0.30	1.80	14.71	3.00	410.00	0.12
		- GREY CHERT FACIES: Consists of laminated medium light grey to medium dark grey chert. Mineralization: 95-99% quartz and up to 5% secondary calcite.	633870	171.20	171.20	0.00	0.01	0.02	1.00	5.00	0.50
			633871	171.20	172.00	0.80	0.27	0.33	1.00	5.00	0.82
			633872	172.00	173.20	1.20	0.18	0.63	1.00	20.00	0.29
		- WHITISH GREY ZN-PB MUDSTONE FACIES: Is a laminated cherty rock containing up to 70% sulphides. Mineralization: quartz, sphalerite and galena are the major minerals with only minor amounts of pyrite and locally calcite. Sedimentary diagenetic structures are common and well displayed in the facies, such as:	633873	173.20	173.70	0.50	0.80	3.82	3.00	110.00	0.21
			633874	173.70	174.10	0.40	1.17	5.90	1.00	160.00	0.20
			633875	174.10	174.70	0.60	1.39	5.37	2.00	140.00	0.26
			633876	174.70	175.10	0.40	0.56	1.40	1.00	40.00	0.40

Selwyn Project Diamond Drill Log

Hole Number:
XYC-224

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
lamination, pseudo-beds, calcite nodules & limestone nodules and abundant water escape structures. Most obvious structure in facies is cross-cutting veins containing massive sphalerite and galena with minor pyrite. They range in width from 0.5 to 10mm. - THIN BEDDED CHERTY MUDSTONE FACIES: Consists of rhythmic intercalated laminae of chert, carbonaceous mudstone and minor micrite. This facies contains significant amounts of Zn and Pb sulphides. - CHERTY MUDSTONE FACIES: Consists of a greyish black monotonous siliceous, carbonaceous mudstone. It is most typically found overlying the thin bedded calcareous mudstone facies. - THIN BEDDED CALCAREOUS MUDSTONE FACIES: Consists of laminated carbonaceous mudstone containing 20-40% calcite, 40-55% quartz and 10-20% muscovite. Sulphides occur in laminae. In the XY area it is usually the lowest facies in the section to contain laminated sulphides. - CALCAREOUS MUDSTONE FACIES: Consists of grey to greyish black monotonous, calcareous siliceous carbonaceous mudstone. There are no feathery calcite beds or pyrite-calcite blebs in the facies, making it easily distinguishable from the CCMS. - GRADED LIMESTONE FACIES: Is a laminated argillaceous limestone with intercalated carbonaceous limestone laminae. The main rock type in the facies is laminated limestone with laminae up to 0.1-7mm thick. - LIGHT GREY BASAL LIMESTONE FACIES - LGLS: Consists of laminated argillaceous limestone. In the Anniv area it marks the end of the ACTM. It's not always present in the stratigraphy. - BASAL FACIES: This is a highly contorted and locally foliated carbonaceous mudstone. Unlike the other facies it is not repeated higher in the member. It			633877	175.10	175.70	0.60	0.75	4.20	1.00	120.00	0.18
			633878	175.70	176.70	1.00	1.41	5.32	3.00	150.00	0.27
			633879	176.70	176.90	0.20	2.86	21.14	6.00	430.00	0.14
			633880	176.90	176.90	0.00	1.39	3.00	18.00	180.00	0.46
			633881	176.90	177.10	0.20	3.22	1.49	1.00	40.00	2.16
			633882	177.10	177.90	0.80	1.99	9.39	1.00	290.00	0.21
			633883	177.90	178.80	0.90	0.09	0.52	1.00	20.00	0.17
			633884	178.80	179.80	1.00	0.21	0.16	1.00	5.00	1.31
			633885	179.80	180.00	0.20	3.55	5.77	1.00	270.00	0.62
			633886	180.00	181.20	1.20	0.33	0.55	1.00	20.00	0.60
			633887	181.20	181.80	0.60	0.17	0.15	1.00	5.00	1.13
			633888	181.80	182.50	0.70	0.55	0.51	1.00	10.00	1.08
			633889	182.50	183.00	0.50	0.06	0.10	1.00	5.00	0.60
			633890	183.00	183.90	0.90	0.62	1.00	1.00	20.00	0.62
			633891	183.00	183.90	0.90	0.14	0.86	1.00	20.00	0.16
			633892	183.90	184.60	0.70	1.15	1.85	3.00	30.00	0.62
			633893	184.60	185.40	0.80	0.33	1.65	1.00	30.00	0.20
			633894	185.40	185.90	0.50	0.34	1.63	1.00	40.00	0.21
			633895	185.90	186.90	1.00	0.25	0.30	1.00	5.00	0.83
			633896	186.90	187.50	0.60	2.27	0.57	3.00	10.00	3.98
			633897	187.50	188.00	0.50	0.09	0.18	1.00	5.00	0.50
			633898	188.00	188.40	0.40	2.10	2.50	9.00	50.00	0.84
			633899	188.40	188.60	0.20	0.14	0.78	1.00	20.00	0.18
			633900	188.60	188.60	0.00	0.01	0.01	1.00	5.00	2.00
			633901	188.60	189.00	0.40	0.43	1.33	3.00	30.00	0.32
			633902	189.00	189.50	0.50	0.07	0.59	1.00	20.00	0.12
			633903	189.50	190.20	0.70	0.06	0.04	1.00	5.00	1.50
			633904	190.20	191.10	0.90	0.32	0.85	4.00	20.00	0.38
			633905	191.10	191.90	0.80	0.03	0.01	1.00	5.00	6.00
			633906	191.90	192.80	0.90	0.01	0.03	2.00	5.00	0.33
			633907	192.80	194.20	1.40	0.55	0.69	4.00	20.00	0.80
			633908	194.20	195.50	1.30	0.01	0.01	1.00	5.00	2.00

Selwyn Project Diamond Drill Log

Hole Number:
XYC-224

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		appears locally to contain the slip zone of a major slump. The facies has only been observed in the YX area. It is 0.1-2m thick. The facies consists of massive carbonaceous siliceous mudstone with lenses and laminae of contorted, slightly carbonaceous chert. « 163.50- 164.10 lam'd metalliferous mdst. Laminae are cross-bedded. Enriched sph laminae, minor interstitial galena » « 164.10- 165.30 Lt grey convol. sph and gal laminae w discordant min'd mud veins. Calcite veins mirror the mud but host broken-up py. Gal ~10%, Sph ~ 20% » « 165.30- 167.20 Slightly wavy laminae lt to med grey w sph. layers, also cal-rich lam's. 2ndary py is ass'd w qtz & cal. Inc's LMST intervals. Pb + Zn ~15% » « 167.20- 170.90 intercalated lmst & carb mdst. LMST is barren to visibly mineralized. Lam'd mdst has py, calcic and sph-enriched laminae. Qtz/cal veins conformable » « 170.90- 171.20 Metalliferous laminated mudstone. Pb ~ 7%, Zn~13% » « 171.20- 173.70 Fine-grained bluish grey limestone, finely laminated. Intercalated with minor carbonaceous mudstone. Limestone is heavily veined with calcite and minor quartz. Pyrite concentrates as blebs in limestone and is often brecciated by calcite. Minor sections of metalliferous mudstone (4-7cm thick) are spaced throughout. Trace blow-outs of coarse galena occur at the lower contact of mudstone with limestone.» « 173.70- 174.70 Planar laminated metalliferous mudstone. Calcite concentrations mark depositional layer boundaries. Blebs of coarse galena (<2%) are 2-4mm thick. Pb ~ 2%, Zn ~ 5.5% » « 174.70- 175.70 Strongly mineralized limestone. Laminated mud-rich limestone with fine-grained sphalerite concentrating in some laminae. Pb ~									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-224

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		1.5%, Zn ~ 4% » « 175.70- 178.80 Highly mixed zone, broken up in terms of lithological abundance. i) Laminated limestone, weakly mineralized with trace sphalerite, contains rounded limestone concretions 4-12cm diameter. ii) Metalliferous mudstone, planar laminae vary to contorted laminae, very high grade in 10-30cm sections. iii) Least common. Low-grade carbonaceous mudstone with abundant conformable calcite veins. Mudstone has many rounded limestone clasts throughout. » « 178.80- 181.20 Calcareous and carbonaceous mudstone with ~10-20% rounded, laminated limestone clasts. Planar and wavy laminated moderately mineralized (Pb+Zn ~2%) mudstone comprises ~5-7% of interval, separated out for sampling where possible. Calcite veining is pervasive.» « 181.20- 181.80 Laminated limestone with muddy sections 10-20 thick, massive pyrite concentrations 3-4cm thick. Abundant rounded limestone clasts. » « 181.80- 182.50 Carbonaceous, metalliferous, laminated limestone. Also, laminated limestone clasts 20cm in diameter are conformable to S0. » « 182.50- 185.90 Mixed limestone and laminated carbonaceous mudstone. Some sections of mudstone are enriched with up to 4% Pb and 15% Zn. Limestone fragments have a conformable foliation to the mudrock. » « 185.90- 188.00 Laminated limestone, barren to mineralization except for trace blebs of galena at depositional boundaries. S0 changes dramatically between depositional boundaries.» « 188.00- 188.40 Laminated dark grey-brown, calcite-rich mudstone. Mineralized with ~2% Zn and 1.5% Pb, only weakly visible laminae. Abundant pyrite in many laminae.» « 188.40- 188.60 Muddy laminated limestone with minor calcite veinlets									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-224

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		and calcite remineralized stylolites. »									
		« 188.60- 189.00 Laminated dark grey-brown, calcite-rich mudstone. Mineralized with ~2% Zn and 1.5% Pb, only weakly visible laminae. Abundant pyrite in many laminae. »									
		« 189.00- 191.10 Black to dark grey carbonaceous mudstone, pyrite pseudobeds, abundant (3-6mm thick) clastic, siliceous and cherty bands. Few rounded, limestone clasts are elongated along S0. »									
		« 191.10- 191.90 Light grey laminated limestone with limestone clasts, thin wispy calcite veins are semi-regular. »									
		« 191.90- 194.20 Black, carbonaceous mudstone, no visible mineralization, abundant calcite veining FLT »« gg 20%»« bx 40%»« Brco 40%»									
		« 194.20- 195.50 Basal limestone, light grey limestone, laminated, elongate limestone clasts are <2% of rock, intrusive coarse grained calcite-quartz <3%. »									
195.50	213.20	CCMS	633909	195.50	196.40	0.90	0.04	0.38	3.00	20.00	0.11
		CCMS – Calcareous Mudstone	633910	196.40	196.40	0.00	6.30	6.86	71.00	190.00	0.92
			633911	196.40	197.40	1.00	0.02	0.05	1.00	5.00	0.40
		Massive, calcareous, carbonaceous, dark grey mudstone. Most of the member is massive, but rare poorly defined bedding and pyrite-calcite micro-concretions are present. Most diagnostic structures are feathery calcite beds (=thin calcite-cemented concretions, many of them contain pyrite cores) and calcite pseudo-beds (= fibrous calcite vein parallel to bedding).									
		« lm ca 5.00-10.00mm », « nodules py -3.00% 2.00-20.00mm »,									
		« General description applies. »									
		< @ 204.60 defined by pyritic and calcic laminae S0, tca 85° >									
213.20	213.20	EOH									

Diamond Drill Log

Comprehensive Report for Hole:

XYC-223

Hole No.: XYC-223	Depth: 650.10 m	Horizontal Length: 0.00 m	Project: 1710
Location Data:			
Property:	Selwyn Project	Claim Name:	X46
Mining District:	Selwyn Basin	Grant Number:	Y 64679
Province/Territory:	Yukon		
UTM Co-Ordinates & Altitude of Drill Hole Collar:			
UTM Easting:	487394.32 m	True Azimuth:	28.0 °
UTM Northing:	6927161.56 m	Hole Angle:	-59.0 °
Elevation (m):	1420.90 m	NTS Name:	Placer Creek
		NTS Number:	105L06
Grid Co-Ordinates of Drill Hole Collar:			
Grid Easting (m):	0.00 m	Grid Name:	HP 06
Grid Northing (m):	0.00 m	Grid Type:	100m
Grid Azimuth:	88.0 °		
Dimond Drilling Contract:			
Drilled By:	NL-03	Date Drilling Start:	6/10/2010
		Date Finish:	18/10/2010
Diamond Drill Core:			
Logged By:	Kate C./Matt J.	Date Logging Start:	25/10/2010
		Date Finish:	5/11/2010
Legend for Core Logging Codes: PAX			
Core Size:	NQ	Cemented:	Yes
Casing Depth:	6.40 m	Casing Pulled:	
Water Depth:	0.00 m	Overburden Depth:	6.40 m
Level:		Section:	
		Drift:	

Selwyn Project

Diamond Drill Log

Survey Data for Hole

XYC-223

Hole Comments:

Wed, Oct 06 ---No drilling last night. Pulled rods, cemented hole and prepared for drill move to target #49,50,51.

=====

Thu, Oct 07 --- At a total depth of 71.02m. Abundant faulting in ACTM from surface up to 43.9m, mostly consisting of fault gouge and breccia with combined Pb/Zn between 1-6%. Still in ACTM at 71.02m.

=====

Fri, Oct 08 --- At a total depth of 163.37m. Patchy zones of up to 0.5% occur in LCMS at current depth.

=====

Sat, Oct 09 --- At a total depth of 256.8m, still in second high grade intersection of ACTM.

=====

Sun, Oct 10 --- At a total depth of 322.5m, still in ACTM with many zones looking high grade.

=====

Mon, Oct 11 ---At a total depth of 404.2m in CCMS. ACTM-CCMS contact at 359.1m.

=====

Tue, Oct 12 --- At a total depth of 458.4m, in FLMD. A major fault between 404.3m - 419.7m causes an unconformity between CCMS and FLMD, placing CCMS above FLMD.

=====

Wed, Oct 13 ---At a total depth of 507.9m, still in FLMD. They will continue drilling today.

=====

Thu, Oct 14 --- At a total depth of 566.3m. Drill has run out of imperial rods at a depth of 1758 feet (535.84m), they have switched over to metric rods from that point on. The rock type is still light grey flaggy mudstone. Bioturbations trend at low angle to core axis (<30 degrees). From approximately 546.3m to 566.3m quartz intrudes and brecciates flaggy mudstone and has since been recrystallized into a hard, competent, siliceous fault breccia zone.

=====

Fri, Oct 15 --- During dayshift yesterday somehow the rods were sheared at one of the joints. They are now attempting to retrieve the rod string with a custom tap. If they are successful in latching on with the tap, they will likely still have to pull rods before going back down. Dayshift yesterday drilled to 586 meters in FLMD.

=====

Sat, Oct 16 --- Yesterday dayshift was successful in using the custom tap to pull the rod string out. However, last night the tube was somehow stuck in the core barrel and could not be pulled out, perhaps due to worn out ball-berrings. They are confident that they can resolve that problem this morning and continue coring today. Last night they drilled several meters before the tube became stuck. Likely FLMD-USMS contact at approximately 588 meters. Generally competent core.

=====

Sun, Oct 17 --- The tube and core that was stuck in the core barrel remains stuck, but they should have that short section of core removed today. Yesterday they began drilling with a new core barrel and tube, and there are no current mechanical problems to report. We hit our third intersection of ACTM at approximately 617 meters; core is relatively competent. At 630 meters now.

Selwyn Project

Diamond Drill Log

Survey Data for Hole

XYC-223

=====

Mon, Oct 18 ---Yesterday dayshift hit the ACTM-CCMS contact at 629 meters, and drilled through 21 meters of footwall to 650 meters. Last night the experienced driller found that the hole had caved in, and could not get down below approximately 500 meters. We are shutting down the hole this morning, and cementing from approximately 500 meters (where the hole is blocked) to surface. This is because putting plugs down would be difficult if not impossible given the overall condition of the hole, and because we have three ACTM intersections over an unusually broad total depth. This drill will be moved several degrees to setup #51 on the same pad, and will commence drilling XYC-233

<i>Depth</i>	<i>Dip</i>	<i>Azimuth</i>
0.00	-59.0	28.0
58.00	-58.3	29.0
93.90	-58.5	30.3
139.60	-56.4	30.9
185.30	-54.9	33.7
231.00	-54.3	31.7
276.80	-53.1	34.0
322.50	-51.7	33.7
368.20	-50.6	36.6
398.70	-50.7	34.5
459.60	-47.6	37.6
520.60	-45.7	39.8
566.30	-43.9	41.5
612.00	-42.9	41.7

Selwyn Project Diamond Drill Log

Hole Number:
XYC-223

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
0.00	6.40	OVBR									
6.40	46.00	FLT	633651	45.10	46.00	0.90					
« Carbonaceous, very significant fault zone. Competent segments are primarily limestone. Breccia fragments are carbonaceous, siliceous mudstone. Material likely derived largely from USMS. » « gg 25% » « bx 60% »											
46.00	111.80	ACTM	633652	46.00	46.40	0.40					
ACTM – Active Member			633653	46.40	47.90	1.50					
The ACTM consists of a repetitive, possibly rhythmic, sequence of intercalated carbonaceous mudstone, cherty mudstone, chert and limestone and locally contains economically significant Zn and Pb sulphides (see bold marked facies), mainly in its sections with well developed lamination. Because of its heterogeneity, the member is distinctive and easily identified. ===== The ACTM has 8 different facies: ===== - GREY CHERT FACIES: Consists of laminated medium light grey to medium dark grey chert. Mineralization: 95-99% quartz and up to 5% secondary calcite. - WHITISH GREY ZN-PB MUDSTONE FACIES: Is a laminated cherty rock containing up to 70% sulphides. Mineralization: quartz, sphalerite and galena are the major minerals with only minor amounts of pyrite and locally calcite. Sedimentary diagenetic structures are common and well displayed in the facies, such as: lamination, pseudo-beds, calcite nodules & limestone nodules and abundant water escape structures. Most obvious structure in facies is cross-cutting veins containing massive sphalerite and galena with minor pyrite. They range in width from 0.5 to 10mm. - THIN BEDDED CHERTY MUDSTONE FACIES: Consists of rhythmic intercalated laminae of chert, carbonaceous mudstone and minor micrite. This facies contains significant amounts of Zn and Pb sulphides.			633654	47.90	48.40	0.50					
			633655	48.40	49.20	0.80					
			633656	49.20	50.30	1.10					
			633657	50.30	50.90	0.60					
			633658	50.90	51.50	0.60					
			633659	51.50	52.10	0.60					
			633660	52.10	52.90	0.80					
			633661	52.10	52.90	0.80					
			633662	52.90	53.40	0.50					
			633663	53.40	53.90	0.50					
			633664	53.90	54.40	0.50					
			633665	54.40	55.40	1.00					
			633666	55.40	56.40	1.00					
			633667	56.40	57.40	1.00					
			633668	57.40	58.20	0.80					
			633669	58.20	59.00	0.80					
			633670	59.00	59.00	0.00					
			633671	59.00	59.60	0.60					
			633672	59.60	60.60	1.00					
			633673	60.60	61.50	0.90					
			633674	61.50	62.30	0.80					
			633675	62.30	63.10	0.80					
			633676	63.10	64.00	0.90					
			633677	64.00	64.60	0.60					
			633678	64.60	65.20	0.60					
			633679	65.20	65.60	0.40					

Selwyn Project Diamond Drill Log

Hole Number:
XYC-223

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
- CHERTY MUDSTONE FACIES: Consists of a greyish black monotonous siliceous, carbonaceous mudstone. It is most typically found overlying the thin bedded calcareous mudstone facies. - THIN BEDDED CALCAREOUS MUDSTONE FACIES: Consists of laminated carbonaceous mudstone containing 20-40% calcite, 40-55% quartz and 10-20% muscovite. Sulphides occur in laminae. In the XY area it is usually the lowest facies in the section to contain laminated sulphides. - CALCAREOUS MUDSTONE FACIES: Consists of grey to greyish black monotonous, calcareous siliceous carbonaceous mudstone. There are no feathery calcite beds or pyrite-calcite blebs in the facies, making it easily distinguishable from the CCMS. - GRADED LIMESTONE FACIES: Is a laminated argillaceous limestone with intercalated carbonaceous limestone laminae. The main rock type in the facies is laminated limestone with laminae up to 0.1-7mm thick. - LIGHT GREY BASAL LIMESTONE FACIES - LGLS: Consists of laminated argillaceous limestone. In the Anniv area it marks the end of the ACTM. It's not always present in the stratigraphy. - BASAL FACIES: This is a highly contorted and locally foliated carbonaceous mudstone. Unlike the other facies it is not repeated higher in the member. It appears locally to contain the slip zone of a major slump. The facies has only been observed in the YX area. It is 0.1-2m thick. The facies consists of massive carbonaceous siliceous mudstone with lenses and laminae of contorted, slightly carbonaceous chert. Abundant limestone in some classic dark grey laminated and light grey high grade ranges. Likely intersecting at a acute angle to bedding, producing much greater appearant thickness then true thickness. Broken up throughout.			633680	65.60	65.60	0.00					
			633681	65.60	66.00	0.40					
			633682	66.00	66.70	0.70					
			633683	66.70	67.50	0.80					
			633684	67.50	68.40	0.90					
			633685	68.40	69.20	0.80					
			633686	69.20	69.60	0.40					
			633687	69.60	70.70	1.10					
			633688	70.70	71.40	0.70					
			633689	71.40	72.30	0.90					
			633690	72.30	72.90	0.60					
			633691	72.30	72.90	0.60					
			633692	72.90	73.70	0.80					
			633693	73.70	74.80	1.10					
			633694	74.80	75.30	0.50					
			633695	75.30	76.10	0.80					
			633696	76.10	76.80	0.70					
			633697	76.80	77.40	0.60					
			633698	77.40	79.20	1.80					
			633699	79.20	80.30	1.10					
			633700	80.30	80.30	0.00					
			633701	80.30	81.40	1.10					
			633702	81.40	82.40	1.00					
			633703	82.40	83.40	1.00					
			633704	83.40	84.00	0.60					
			633705	84.00	85.60	1.60					
			633706	85.60	86.60	1.00					
			633707	86.60	87.60	1.00					
			633708	87.60	89.10	1.50					
			633709	89.10	90.00	0.90					
			633710	90.00	90.00	0.00					
			633711	90.00	90.80	0.80					
			633712	90.80	91.50	0.70					

Selwyn Project

Diamond Drill Log

Hole Number:
XYC-223

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

[illegible]

Selwyn Project Diamond Drill Log

Hole Number:
XYC-223

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		pitted texture, weakly mineralized. One <1cm thick galena veinlette observed. » « 59.90- 60.10 Fault zone. » « gg 10%» « bx 90%» « 60.60- 61.50 Broken up, siliceous, weakly laminated mudstone. Weak mineralization. » « 61.50- 62.30 Classic high grade appearance. Light grey, strongly mineralized, siliceous, strongly laminated, laminae offset by secondary foliation. Estimated 20% combined galena and sphalerite. Sphalerite nodules <1cm observed. » « 62.30- 63.20 Light-medium grey, laminated calcareous mudstone. Weak to moderate mineralization. » « 63.20- 64.00 Very broken up. Unlaminated, weakly mineralized, calcareous mudstone. » « 64.00- 64.60 High grade appearance. Light grey siliceous mudstone. Strongly mineralized. Galena infill visible in spaced secondary foliation planes. » « 64.60- 66.00 Moderate mineralization. Dark grey, laminated calcareous mudstone interbedded with light grey limestone. Galena veinlettes visible. » « 66.00- 67.50 Light grey limestone, weakly laminated with minor dark grey calcareous mudstone. Strongly laminated. Weakly mineralized overall. » « 67.50- 69.20 Fault zone - fragments primarily weakly laminated calcareous mudstone with minor limestone. Weak mineralization. » « gg 5%» « bx 60%» « 69.20- 69.60 Light grey, siliceous mudstone. Strong mineralization, pitted texture, weakly laminated. Galena veinlettes visible. »									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-223

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		« 69.60- 74.80 Very broken up. Laminated calcareous mudstone. Low grade mineralization overall. »									
		« 74.80- 75.30 Light grey limestone. Weak mineralization. »									
		« 75.30- 77.40 Broken up. Calcareous mudstone with minor limestone. Laminated locally with weak to moderate mineralization overall. »									
		« 77.40- 82.40 Competent, light grey limestone, laminated with minor dark grey calcareous mudstone. Low grade mineralization overall. »									
		« 82.40- 87.60 Totally broken up. Primarily unlaminated calcareous mudstone with minor competent segments (<30cm) of light grey limestone. Very low grade mineralization overall. »									
		« 87.60- 90.00 Light grey laminated limestone. Non to weakly mineralized. »									
		« 90.00- 90.80 Medium grey, unlaminated, "pitted", weakly calcareous mudstone. Weakly mineralized. »									
		« 90.80- 93.20 Light grey limestone, "pitted", no visible mineralization, unlaminated. »									
		« 93.20- 94.30 Weakly calcareous dark grey mudstone, unlaminated with minor light grey laminated limestone. non to weakly mineralized. »									
		« 94.30- 95.60 Weakly laminated, "pitted", limestone in minor calcareous mudstone. non to weakly mineralized. »									
		« 95.60- 97.40 Strongly calcareous, unlaminated mudstone with light-medium grey limestone. non to weakly mineralized. »									
		« 97.40- 101.60 Light grey, laminated limestone breccia. No visible									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-223

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		mineralization. » « 101.60- 101.90 Competent calcareous mudstone with limestone breccia. No visible mineralization. » « 101.90- 102.30 Laminated calcareous mudstone with pitted texture and minor limestone. Showing weak mineralization » « 102.30- 102.80 Light grey, siliceous, strongly laminated mudstone showing typical high grade appearance with secondary foliation. Strong visible mineralization. Visible galena veinlettes throughout. » « 102.80- 103.50 Light-medium grey , laminated limestone showing weak to moderate mineralization. » « 103.50- 106.40 Weakly laminated, "pitted", calcareous mudstone showing low grade mineralization. » « 106.40- 110.30 Medium grey, laminated limestone breccia with minor calcareous mudstone. Showing low grade mineralization throughout. » « 110.30- 110.60 Strongly laminated limestone showing moderate mineralization. » « 110.60- 111.80 Broken up. Weakly laminated calcareous mudstone. »									
111.80	182.20	USMS	633738	181.50	182.20	0.70					
		USMS – Upper Siliceous Mudstone Consists of interlaminated dark grey to black mudstone and light to medium grey chert. Regionally, a 1m thick graptolite zone occurs 15m below the top of the upper unit, this is usable as a horizon. The USMS is divided into 3 units. The Lower Unit contains abundant limestone concretions and Galena and sphalerite micro-concretions occur locally near the base of this unit. « gra , lm chrt -20.00% », « cg xtl sph crns ca 5.00-20.00cm », « bed chrt 10.00-15.00% »,									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-223

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
<i>Back into this unit without a fault, likely due to a minor synclinal fold.</i> <i>Typical lithology, through as expected resembles Upper Siliceous Mudstone immediately above Active Member throughout with prevalent "pitted" texture.</i> « 112.70- 118.00 Very broken up. » « @ 124.20 Defined by planer parallel chert bands. S0 tca 20° » « 124.30- 134.00 Very broken up. » « 134.00- 136.00 Fault » « gg 5% » « bx 50% » « 144.40- 147.80 Fault » « bx 60% » « @ 154.50 Compositional contact between medium grey and dark grey siliceous mudstone. S0 tca 13° » « @ 164.60 Carbonaceous bed within medium grey siliceous mudstone. S0 tca 38° » « @ 165.60 Planer parallel chert bands S0 tca 39° » « 170.80- 171.50 Fault » « gg 5% » « bx 70% » « 174.40- 180.20 Fault zone » « gg 5% » « bx 30% » « brco 50% »											
182.20	252.50	ACTM	633739	182.20	182.50	0.30					
ACTM – Active Member			633740	182.50	182.50	0.00					
			633741	182.50	182.90	0.40					
			633742	182.90	183.20	0.30					
			633743	183.20	183.60	0.40					
			633744	183.60	183.90	0.30					
			633745	183.90	184.70	0.80					
			633746	184.70	185.60	0.90					
<i>The ACTM consists of a repetitive, possibly rhythmic, sequence of intercalated carbonaceous mudstone, cherty mudstone, chert and limestone and locally contains economically significant Zn and Pb sulphides (see bold marked facies), mainly in its sections with well developed lamination. Because of its heterogeneity, the member is distinctive and easily identified.</i>											

Selwyn Project Diamond Drill Log

Hole Number:
XYC-223

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
=====			633747	185.60	186.60	1.00					
			633748	186.60	187.70	1.10					
The ACTM has 8 different facies:			633749	187.70	188.80	1.10					
=====			633750	188.80	198.30	9.50					
			633751	188.80	189.30	0.50					
- GREY CHERT FACIES: Consists of laminated medium light grey to medium dark grey chert. Mineralization: 95-99% quartz and up to 5% secondary calcite.			633752	189.30	189.80	0.50					
			633753	189.80	190.90	1.10					
			633754	190.90	191.30	0.40					
- WHITISH GREY ZN-PB MUDSTONE FACIES: Is a laminated cherty rock containing up to 70% sulphides. Mineralization: quartz, sphalerite and galena are the major minerals with only minor amounts of pyrite and locally calcite. Sedimentary diagenetic structures are common and well displayed in the facies, such as: lamination, pseudo-beds, calcite nodules & limestone nodules and abundant water escape structures. Most obvious structure in facies is cross-cutting veins containing massive sphalerite and galena with minor pyrite. They range in width from 0.5 to 10mm.			633755	191.30	192.50	1.20					
			633756	192.50	192.80	0.30					
			633757	192.80	193.10	0.30					
			633758	193.10	193.90	0.80					
			633759	193.90	194.70	0.80					
			633760	194.70	194.70	0.00					
			633761	194.70	195.00	0.30					
			633762	195.00	195.30	0.30					
			633763	195.30	196.30	1.00					
- THIN BEDDED CHERTY MUDSTONE FACIES: Consists of rhythmic intercalated laminae of chert, carbonaceous mudstone and minor micrite. This facies contains significant amounts of Zn and Pb sulphides.			633764	196.30	197.20	0.90					
			633765	197.20	198.00	0.80					
			633766	198.00	198.90	0.90					
- CHERTY MUDSTONE FACIES: Consists of a greyish black monotonous siliceous, carbonaceous mudstone. It is most typically found overlying the thin bedded calcareous mudstone facies.			633767	198.90	199.80	0.90					
			633768	199.80	200.60	0.80					
			633769	200.60	201.20	0.60					
			633770	201.20	201.20	0.00					
			633771	201.20	201.90	0.70					
- THIN BEDDED CALCAREOUS MUDSTONE FACIES: Consists of laminated carbonaceous mudstone containing 20-40% calcite, 40-55% quartz and 10-20% muscovite. Sulphides occur in laminae. In the XY area it is usually the lowest facies in the section to contain laminated sulphides.			633772	201.90	202.30	0.40					
			633773	202.30	202.80	0.50					
			633774	202.80	203.50	0.70					
			633775	203.50	204.40	0.90					
			633776	204.40	205.20	0.80					
- CALCAREOUS MUDSTONE FACIES: Consists of grey to greyish black monotonous, calcareous siliceous carbonaceous mudstone. There are no feathery calcite beds or pyrite-calcite blebs in the facies, making it easily distinguishable from			633777	205.20	206.60	1.40					
			633778	206.60	207.50	0.90					
			633779	207.50	208.50	1.00					

Selwyn Project Diamond Drill Log

Hole Number:
XYC-223

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
the CCMS.			633780	208.50	209.50	1.00					
			633781	208.50	209.50	1.00					
- GRADED LIMESTONE FACIES: Is a laminated argillaceous limestone with intercalated carbonaceous limestone laminae. The main rock type in the facies is laminated limestone with laminae up to 0.1-7mm thick.			633782	209.50	210.30	0.80					
			633783	210.30	210.80	0.50					
			633784	210.80	211.40	0.60					
			633785	211.40	212.40	1.00					
- LIGHT GREY BASAL LIMESTONE FACIES - LGLS: Consists of laminated argillaceous limestone. In the Anniv area it marks the end of the ACTM. It's not always present in the stratigraphy.			633786	212.40	213.30	0.90					
			633787	213.30	214.40	1.10					
			633788	214.40	215.30	0.90					
- BASAL FACIES: This is a highly contorted and locally foliated carbonaceous mudstone. Unlike the other facies it is not repeated higher in the member. It appears locally to contain the slip zone of a major slump. The facies has only been observed in the YX area. It is 0.1-2m thick. The facies consists of massive carbonaceous siliceous mudstone with lenses and laminae of contorted, slightly carbonaceous chert.			633789	215.30	216.10	0.80					
			633790	216.10	216.10	0.00					
			633791	216.10	217.10	1.00					
			633792	217.10	217.60	0.50					
			633793	217.60	218.10	0.50					
			633794	218.10	218.50	0.40					
			633795	218.50	218.90	0.40					
			633796	218.90	219.50	0.60					
Long intersection, acute core to bedding angle. Notable high grade ranges. Generally competent.			633797	219.50	219.90	0.40					
			633798	219.90	220.20	0.30					
			633799	220.20	220.70	0.50					
« 182.20- 182.50 Dark grey, unlaminated mudstone with trace mineralization. »			633800	220.70	220.70	0.00					
			635501	220.70	221.20	0.50					
			635502	221.20	221.80	0.60					
« 182.50- 182.90 Medium grey, strongly laminated siliceous mudstone with moderate grade mineralization. »			635503	221.80	222.80	1.00					
			635504	222.80	223.20	0.40					
			635505	223.20	224.60	1.40					
« 182.90- 183.20 Weakly laminated, dark grey, siliceous mudstone with low grade mineralization. »			635506	224.60	225.30	0.70					
			635507	225.30	225.90	0.60					
			635508	225.90	226.40	0.50					
« 183.20- 183.60 Light grey, strongly laminated, siliceous mudstone. Moderate to high grade mineralization. »			635509	226.40	226.90	0.50					
			635510	226.90	227.70	0.80					
			635511	226.90	227.70	0.80					
« 183.60- 183.90 Very broken up, laminated, dark grey, siliceous mudstone. Low to moderate mineralization. »			635512	227.70	228.00	0.30					
			635513	228.00	228.50	0.50					

Selwyn Project Diamond Drill Log

Hole Number:
XYC-223

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
« 183.90- 184.70 Silicified, unlaminated mudstone. Non to weakly laminated. » « 184.70- 187.70 Primarily laminated, dark grey, siliceous mudstone with minor limestone and low grade mineralization. » « 187.70- 188.80 Coarser, strongly laminated, medium grey, siliceous siltstone with abundant calcite veining and low grade mineralization. » « 188.80- 189.30 Coarser, dark grey, strongly laminated siltstone with moderate mineralization and abundant pyrite nodules. » « 189.30- 189.80 Coarser, light grey siliceous mudstone, brecciated appearance. Moderate to high grade mineralization. » « 189.80- 190.90 Dark grey, laminated siliceous mudstone with moderate mineralization. Classic active member. Includes minor limestone. » « 190.90- 191.30 Breccia containing angular fragments (1-7cm) of very high grade, laminated active member within a matrix of very dark grey siliceous, laminated mudstone. Includes minor limestone and abundant calcite veins. Moderate to high grade mineralization overall. » « 191.30- 192.50 Dark grey, laminated siliceous mudstone breccia with minor limestone and abundant micro-calcite veins. Moderate to high grade mineralization. » « 192.50- 192.80 Light grey, unlaminated limestone with minor medium grey laminated siliceous mudstone. Low grade mineralization overall. » « 192.80- 193.10 Primarily light grey, high grade, brecciated, siliceous mudstone with minor dark grey, brecciated, siliceous mudstone. High grade mineralization overall. »			635514	228.50	229.40	0.90					
			635515	229.40	230.70	1.30					
			635516	230.70	232.10	1.40					
			635517	232.10	233.50	1.40					
			635518	233.50	234.90	1.40					
			635519	234.90	236.10	1.20					
			635520	234.90	234.90	0.00					
			635521	236.10	237.60	1.50					
			635522	237.60	238.90	1.30					
			635523	238.90	239.40	0.50					
			635524	239.40	240.60	1.20					
			635525	240.60	241.40	0.80					
			635526	241.40	242.90	1.50					
			635527	242.90	243.90	1.00					
			635528	243.90	245.00	1.10					
			635529	245.00	246.50	1.50					
			635530	245.00	245.00	0.00					
			635531	246.50	247.80	1.30					
			635532	247.80	249.40	1.60					
			635533	249.40	250.00	0.60					
			635534	250.00	250.90	0.90					
			635535	250.90	252.50	1.60					

Selwyn Project Diamond Drill Log

Hole Number:
XYC-223

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		« 193.10- 194.70 Classic active member. Dark grey, weakly calcareous, strongly laminated mudstone. Medium grade mineralization overall. »									
		« 194.70- 195.00 Siliceous mudstone, primarily light grey due to high grade mineralization. Includes minor dark grey unlaminated mudstone. High grade mineralization overall. »									
		« 195.00- 195.30 Dark grey, weakly laminated siliceous mudstone showing "pitted" texture. Low grade mineralization overall. »									
		« 195.30- 196.30 Laminated calcareous mudstone with minor limestone and abundant calcite veins. Low grade mineralization overall. »									
		« 196.30- 197.20 Light grey limestone. No visible mineralization. »									
		« 197.20- 201.90 Classic, light grey, high grade, siliceous mudstone with visible galena and sphalerite nodules throughout. Off scale mineralization per Niton. »									
		« 201.90- 202.30 Light grey limestone. »									
		« 202.30- 203.50 Brecciated, siliceous, medium to light grey mudstone with minor limestone. Moderate to high grade mineralization overall. »									
		« 203.50- 205.20 Brecciated. "pitted". siliceous mudstone with low grade mineralization. »									
		« 205.20- 209.50 Unlaminated, dark grey, siliceous mudstone. No visible mineralization. »									
		« 209.50- 210.80 Weakly laminated siliceous mudstone. Laminae not defined by mineralization but by chert, fine grained, and fine grained quartz. »									
		« 210.80- 211.40 Dark grey, unlaminated, siliceous mudstone with no visible mineralization. »									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-223

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		« 211.40- 214.40 Medium to dark grey, unlaminated, siliceous mudstone with "pitted" texture, occuring with minor light grey limestone. No visible mineralization. »									
		« 214.40- 215.30 Medium to dark grey, unlaminated, "pitted", cherty breccia. No visible mineralization. »									
		« 215.30- 216.10 Light grey, weakly laminated limestone. »									
		« 216.10- 217.10 Medium to dark grey, unlaminated, "pitted", cherty breccia. »									
		« 217.10- 218.10 Dark grey, laminated, siliceous mudstone. Moderate mineralization. »									
		« 218.10- 218.50 High grade. Light grey siliceous mudstone. Brecciated with laminated clasts/matrix and visible sphalerite and galena nodules throughout. »									
		« 218.50- 218.90 Light grey limestone with abundant large calcite veins. Low grade mineralization. »									
		« 218.90- 219.50 Primarily calcite-quartz veining with minor laminated, light grey, mineralized siliceous mudstone. »									
		« 219.50- 220.70 High grade active member. Light grey laminated, brecciated, competent, siliceous with sphalerite and galena mineralization making up the bulk of the c ore. Sphalerite and galena crystals/nodules visible throughout. »									
		« 220.70- 221.80 Dark grey, laminated calcareous mudstone with low to medium grade mineralization. »									
		« 221.80- 222.80 Dark grey, weakly laminated, calcareous mudstone. Low									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-223

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		grade mineralization. Very broken up. »									
		« 222.80- 223.20 Medium grey siliceous mudstone with calcite stringers and abundant disseminated pyrite. »									
		« 223.20- 224.60 Weakly calcareous, dark grey mudstone with limestone clasts or concretions. Laminae containing sphalerite. Weak mineralization. »									
		« 224.60- 225.30 Medium grey siliceous mudstone with visible traces of galena. »									
		« 225.30- 226.40 Light grey laminated siliceous mudstone and limestone. Mainly sphalerite. »									
		« 226.40- 226.90 Light grey. mineralized limestone. Some sphalerite and galena. »									
		« 226.90- 227.70 Light grey, silicified mudstone with some limestone. High grade mineralization. Visual sphalerite in laminae and galena in veins =>30%. Brecciated appearance. »									
		« 227.70- 228.00 Mineralized limestone. Fine to medium grained with internal laminae. Low grade by visual inspection. Encrusting pale green fracture infilled with zincite? »									
		« 228.00- 228.50 Light grey, siliceous mudstone. Has encrusting pale/faded green mineral infill in fractures, zincite?. Visible galena. »									
		« 228.50- 229.40 Limestone. Coarse grained, light grey, massive with possible traces of thick internal bedding. Sharp contacts. »									
		« 229.40- 234.90 Weakly laminated, medium to dark grey mudstone. Variably calcareous. Traces of sphalerite visible. Some disseminated pyrite. »									
		« 234.90- 241.40 Dark grey to black mudstone with clacareous/limestone									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-223

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		laminae. Variably calcareous. No visible mineralization. » « 241.40- 245.00 Limestone with abundant calcite veins. No visible mineralization except pyrite blebs associated with calcite. » « 245.00- 247.80 Black mudstone with light grey calcareous laminae and calcite stringers. Some sphalerite laminae. Galena in veins and associated with calcite. » « 247.80- 249.40 Limestone with sphalerite laminae and galena veins. » « 249.40- 250.10 Dark grey mudstone and calcareous laminated mudstone breccia. Calcite stringers with well formed infill crystals in some fractures. » « 250.10- 252.50 Coarse grained limestone with abundant calcite veins. Possible sphalerite. »									
252.50	260.10	FLT									
		« Fault » « gg 20% » « bx 30% » « brco 10% »									
		Material is barren of mineralization and appears to be Upper Siliceous Mudstone. Tested with Niton, no mineralization.									
260.10	275.20	USMS	635536	273.00	273.90	0.90					
		USMS – Upper Siliceous Mudstone	635537	273.90	275.20	1.30					
		Consists of interlaminated dark grey to black mudstone and light to medium grey chert. Regionally, a 1m thick graptolite zone occurs 15m below the top of the upper unit, this is usable as a horizon. The USMS is divided into 3 units. The Lower Unit contains abundant limestone concretions and Galena and sphalerite micro-concretions occur locally near the base of this unit. « gra , lm chrt -20.00% » , « cg xtl sph crns ca 5.00-20.00cm » , « bed chrt 10.00-15.00% » , Faulted back into typical, barren, Upper Siliceous Mudstone with cherty banding.									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-223

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
275.20	337.50	ACTM									
ACTM – Active Member			635538	275.20	276.40	1.20					
			635539	276.40	276.80	0.40					
			635540	276.80	277.80	1.00					
			635541	276.80	277.80	1.00					
			635542	277.80	279.40	1.60					
			635543	279.40	279.90	0.50					
			635544	279.90	280.20	0.30					
			635545	280.20	280.70	0.50					
			635546	280.70	280.90	0.20					
			635547	280.90	281.70	0.80					
			635548	281.70	282.30	0.60					
			635549	282.30	283.20	0.90					
			635550	282.30	282.30	0.00					
			635551	282.30	284.80	2.50					
			635552	284.80	285.60	0.80					
			635553	285.60	287.10	1.50					
			635554	287.10	287.90	0.80					
			635555	287.90	289.50	1.60					
			635556	289.50	291.00	1.50					
			635557	291.00	291.90	0.90					
			635558	291.90	293.60	1.70					
			635559	293.60	295.10	1.50					
			635560	295.10	295.10	0.00					
			635561	295.10	296.10	1.00					
			635562	296.10	296.40	0.30					
			635563	296.40	298.80	2.40					
			635564	298.80	300.30	1.50					
			635565	300.30	303.00	2.70					
			635566	303.00	304.70	1.70					
			635567	304.70	305.00	0.30					
			635568	305.00	306.50	1.50					
			635569	306.50	308.10	1.60					
			635570	308.10	309.70	1.60					
			635571	308.10	309.70	1.60					

The ACTM consists of a repetitive, possibly rhythmic, sequence of intercalated carbonaceous mudstone, cherty mudstone, chert and limestone and locally contains economically significant Zn and Pb sulphides (see bold marked facies), mainly in its sections with well developed lamination. Because of its heterogeneity, the member is distinctive and easily identified.

=====

The ACTM has 8 different facies:

=====

- **GREY CHERT FACIES:** Consists of laminated medium light grey to medium dark grey chert. Mineralization: 95-99% quartz and up to 5% secondary calcite.

- **WHITISH GREY ZN-PB MUDSTONE FACIES:** Is a laminated cherty rock containing up

to 70% sulphides. Mineralization: quartz, sphalerite and galena are the major minerals with only minor amounts of pyrite and locally calcite. Sedimentary diagenetic structures are common and well displayed in the facies, such as: lamination, pseudo-beds, calcite nodules & limestone nodules and abundant water escape structures. Most obvious structure in facies is cross-cutting veins containing massive sphalerite and galena with minor pyrite. They range in width from 0.5 to 10mm.

- **THIN BEDDED CHERTY MUDSTONE FACIES:** Consists of rhythmic intercalated laminae of chert, carbonaceous mudstone and minor micrite. This facies contains significant amounts of Zn and Pb sulphides.

- **CHERTY MUDSTONE FACIES:** Consists of a greyish black monotonous siliceous, carbonaceous mudstone. It is most typically found overlying the thin bedded calcareous mudstone facies.

- **THIN BEDDED CALCAREOUS MUDSTONE FACIES:** Consists of laminated

Selwyn Project Diamond Drill Log

Hole Number:
XYC-223

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
carbonaceous mudstone containing 20-40% calcite, 40-55% quartz and 10-20% muscovite. Sulphides occur in laminae. In the XY area it is usually the lowest facies in the section to contain laminated sulphides. - CALCAREOUS MUDSTONE FACIES: Consists of grey to greyish black monotonous, calcareous siliceous carbonaceous mudstone. There are no feathery calcite beds or pyrite-calcite blebs in the facies, making it easily distinguishable from the CCMS. - GRADED LIMESTONE FACIES: Is a laminated argillaceous limestone with intercalated carbonaceous limestone laminae. The main rock type in the facies is laminated limestone with laminae up to 0.1-7mm thick. - LIGHT GREY BASAL LIMESTONE FACIES - LGLS: Consists of laminated argillaceous limestone. In the Anniv area it marks the end of the ACTM. It's not always present in the stratigraphy. - BASAL FACIES: This is a highly contorted and locally foliated carbonaceous mudstone. Unlike the other facies it is not repeated higher in the member. It appears locally to contain the slip zone of a major slump. The facies has only been observed in the YX area. It is 0.1-2m thick. The facies consists of massive carbonaceous siliceous mudstone with lenses and laminae of contorted, slightly carbonaceous chert. Back into Active Member. « 275.20- 276.40 Medium to dark grey mudstone. Sphalerite laminae and possible traces of galena in veins. » « 276.40- 276.80 Light to medium grey limestone. No visible mineralization. » « 276.80- 279.50 Medium grey siliceous mudstone. Sphalerite laminae											
			635572	309.70	310.40	0.70					
			635573	310.40	310.80	0.40					
			635574	310.80	312.80	2.00					
			635575	312.80	313.20	0.40					
			635576	313.20	314.40	1.20					
			635577	314.40	315.10	0.70					
			635578	315.10	315.60	0.50					
			635579	315.60	316.20	0.60					
			635580	315.60	315.60	0.00					
			635581	316.20	317.60	1.40					
			635582	317.60	318.90	1.30					
			635583	318.90	319.20	0.30					
			635584	319.20	319.50	0.30					
			635585	319.50	321.40	1.90					
			635586	321.40	323.40	2.00					
			635587	323.40	324.90	1.50					
			635588	324.90	326.00	1.10					
			635589	326.00	326.70	0.70					
			635590	326.70	326.70	0.00					
			635591	326.70	328.00	1.30					
			635592	328.00	329.50	1.50					
			635593	329.50	331.00	1.50					
			635594	331.00	331.60	0.60					
			635595	331.60	332.30	0.70					
			635596	332.30	333.80	1.50					
			635597	333.80	334.70	0.90					
			635598	334.70	335.60	0.90					
			635599	335.60	336.60	1.00					
			635600	336.60	337.50	0.90					
			635601	336.60	337.50	0.90					

Selwyn Project Diamond Drill Log

Hole Number:
XYC-223

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		abundant. Some lighter grey sections might be caused by galena dissemination. Zones of pyrite-calcite breccia. » « 279.50- 279.90 Light grey, coarse grained, massive limestone. No visible mineralization. » « 279.90- 280.20 Medium to dark grey mudstone. Sphalerite laminae and possible traces of galena in veins. » « 280.20- 280.70 Limestone concretions. Very faint concentric bedding. No visible mineralization. » « 280.70- 208.90 Medium to dark grey mudstone. Sphalerite laminae and possible traces of galena in veins. » « 280.90- 281.70 Coarse, granular limestone. Faint internal lamination. Appears to be a clast. No visible mineralization. » « 281.70- 285.60 Medium to dark grey mudstone. Sphalerite laminae and possible traces of galena in veins. » « 285.60- 281.90 Medium to light grey, coarse grained limestone. Faint internal structure (laminae?). Abundant calcite veining. No visible mineralization. » « 281.90- 291.00 Light grey silicified mudstone with high grade mineralization. Sphalerite laminae and galena in veins and laminae. 30-40% combined? Laminae are highly deformed - typical looking for high grade. Pyrite-calcite breccia veins. Moderate to low calcite veining. » « 291.00- 291.90 Dark grey to black mudstone with good sphalerite laminae. 10% Zn? » « 291.00- 291.70 Fault - core lost, only 30cm recovered. »									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-223

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		« 291.90- 295.10 Light grey silicified mudstone with high grade mineralization. Sphalerite laminae and galena in veins and laminae. 30-40% combined? Laminae are highly deformed - typical looking for high grade. Pyrite-calcite breccia veins. Moderate to low calcite veining. »									
		« 295.10- 296.10 Darker mudstone. Medium to dark grey before mineralization, sphalerite laminae and galena veins make it lighter grey. 15-20% combined mineralization. »									
		« 296.10- 296.40 Calcite vein. No visible mineralization. »									
		« 296.40- 298.80 Very siliceous, darker mudstone. Medium to dark grey before mineralization, sphalerite laminae and galena veins make it lighter grey. 10% combined min »									
		« 296.50- 297.40 Fault - core lost, almost zero recovery. »									
		« 298.80- 304.70 Dark grey to black mudstone. Weak laminae with some sphalerite. Unit very broken. »									
		« 299.50- 304.70 Fault - slicken slided surfaces present. » « gg 20%» « bx 55%» « brco 10%»									
		« 304.70- 305.00 Light grey, siliceous mudstone with galena veins visible. »									
		« 305.00- 308.60 Medium grey mudstone with sphalerite laminae and galena in small blebs and sometimes in laminae. Combined 10-15% mineralization. Veins of pyrite-calcite breccia. »									
		« 308.60- 309.70 Light to medium grey limestone with abundant calcareous stringers. No visible nimeralization. »									
		« 308.10- 308.60 Fault - less then 5cm recovery. » « gg 10%» « bx 90%»									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-223

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		« 309.70- 310.80 Light grey, siliceous mudstone with sphalerite and lots of galena. 25% combined. »									
		« 310.80- 312.80 Medium grey mudstone with sphalerite laminae and galena in small blebs and sometimes in laminae. Combined 10-15% mineralization. Veins of pyrite-calcite breccia. Whole unit is very broken up. »									
		« 310.80- 312.80 Fault » « gg 20% » « bx 30% » « brco 50% »									
		« 312.80- 313.20 Medium grey, coarse grained, massive limestone. No visible mineralization. »									
		« 313.20- 314.40 Black, laminated, carbonaceous, mudstone. Minor sphalerite mineralization. »									
		« 313.20- 313.90 Fault » « gg 30% » « bx 40% » « brco 30% »									
		« 314.40- 315.10 Light grey, coarse grained, massive limestone. No visible mineralization. Lots of calcite veining. »									
		« 315.10- 315.60 Barren. Dark grey mudstone. »									
		« 315.60- 316.20 Light grey limestone and calcareous mudstone. No visible mineralization. »									
		« 316.20- 318.90 Medium grey mudstone. Good grade mineralization, sphalerite laminae, galena in laminae and veins. 20% combined mineralization. Silicified. Pyrite-calcite breccia veins. »									
		« 318.90- 319.20 Light to medium grey, coarse grained, massive limestone. Calcite veining. No visible mineralization. »									
		« 319.20- 319.50 Dark grey silicified mudstone with spidery calcite veins. Minor sphalerite and galena. »									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-223

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
« 319.50- 321.40 Medium to dark grey, calcareous mudstone and limestone concretions. Weak sphalerite laminations. »											
« 321.40- 323.40 Dark grey to black siliceous mudstone with moderate sphalerite laminae. »											
« 323.40- 324.90 Light grey limestone with intense calcite veining and internal laminations. »											
« 324.90- 326.70 Medium grey, calcareous mudstone with low grades. »											
« 326.70- 328.00 Medium grey siliceous mudstone with low grades. »											
« 328.00- 331.00 Light grey limestone. »											
« 331.00- 331.60 Medium grey, siliceous mudstone with low grades. »											
« 331.60- 332.30 Barren. Black siliceous mudstone. »											
« 332.30- 334.70 Medium grey limestone. »											
« 334.70- 336.60 Barren. Medium grey siliceous mudstone. »											
« 336.60- 337.50 Light grey limestone. »											
337.50	398.00	CCMS	635602	337.50	338.50	1.00					
CCMS – Calcareous Mudstone			635603	338.50	340.00	1.50					
Massive, calcareous, carbonaceous, dark grey mudstone. Most of the member is massive, but rare poorly defined bedding and pyrite-calcite micro-concretions are present. Most diagnostic structures are feathery calcite beds (=thin calcite-cemented concretions, many of them contain pyrite cores) and calcite pseudo-beds (= fibrous calcite vein parallel to bedding).											
« 1m ca 5.00-10.00mm », « nodules py -3.00% 2.00-20.00mm »,											

Selwyn Project Diamond Drill Log

Hole Number:
XYC-223

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		Black calcareous mudstone with faint pyrite beds, locally it looks like Backside Siliceous Mudstone. « 337.50- 341.40 Fault - black calcareous mudstone. » « gg 20%» « bx 30%» « brco 40%» « 344.80- 346.30 Fault » « gg 20%» « bx 40%» « brco 40%» « 367.70- 387.50 Fault » « gg 10%» « bx 10%» « brco 80%»									
398.00	419.40	FLT									
		« 398.00- 419.40 Fault - black calcareous mudstone. » « gg 20%» « bx 40%» « brco 20%»									
419.40	581.10	FLMD									
		FLMD – Flaggy Mudstone Formation Dark grey mudstone in the upper portions of the unit grading into light grey mudstone to siltstone. Contains abundant wispy bioturbation which ranges from randomly-oriented at the top of the unit to bedding-parallel throughout the majority of the unit. Darker upper section has a strong fetid odour along broken surfaces. « btrb 0.10-2.00cm », « cg xtl crns ca 1.00-5.00% 5.00-150.00cm », « crns py 1.00-5.00% 0.10-0.50mm », Medium grey siliceous mudstone with black stretches. « 445.60- 497.60 Whitish grey sections due to the lack of black stretches. » < @ 440.40 Defined on a black band with faint stretches, locally the long axis of two pyrite nodules perpendicular to black stretches S0 tca 45° > « 517.90- 520.60 Medium grey, calcareous mudstone with faint very fine grained pyrite laminae. » « 560.20- 568.10 Matrix supported breccia with medium grey FLMD clasts, the matrix consists of quartz and calcite. »									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-223

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
581.10	615.90	USMS	635604	615.30	615.90	0.60					
<i>USMS – Upper Siliceous Mudstone</i> <i>Consists of interlaminated dark grey to black mudstone and light to medium grey chert. Regionally, a 1m thick graptolite zone occurs 15m below the top of the upper unit, this is usable as a horizon. The USMS is divided into 3 units. The Lower Unit contains abundant limestone concretions and Galena and sphalerite micro-concretions occur locally near the base of this unit. « gra , lm chrt -20.00% », « cg xtl sph crns ca 5.00-20.00cm », « bed chrt 10.00-15.00% »,</i> <i>Black siliceous mudstone with medium grey cherty bands.</i> <i>« 586.30- 588.10 Fault - black mudstone » « gg 5%» « bx 20%» « brco 65%»</i> <i>« 614.20- 615.90 Fault - black mudstone » « gg 10%» « bx 10%» « brco 80%»</i>											
615.90	627.50	ACTM	635605	615.90	617.40	1.50					
<i>ACTM – Active Member</i> <i>The ACTM consists of a repetitive, possibly rhythmic, sequence of intercalated carbonaceous mudstone, cherty mudstone, chert and limestone and locally contains economically significant Zn and Pb sulphides (see bold marked facies), mainly in its sections with well developed lamination. Because of its heterogeneity, the member is distinctive and easily identified.</i> <i>=====</i> <i>The ACTM has 8 different facies:</i> <i>=====</i> <i>- GREY CHERT FACIES: Consists of laminated medium light grey to medium dark grey chert. Mineralization: 95-99% quartz and up to 5% secondary calcite.</i> <i>- WHITISH GREY ZN-PB MUDSTONE FACIES: Is a laminated cherty rock containing</i>			635606	617.40	618.90	1.50					
			635607	618.90	620.00	1.10					
			635608	620.00	620.90	0.90					
			635609	620.90	621.70	0.80					
			635610	621.70	621.70	0.00					
			635611	621.70	623.20	1.50					
			635612	623.20	623.60	0.40					
			635613	623.60	624.10	0.50					
			635614	624.10	625.00	0.90					
			635615	625.00	626.10	1.10					
			635616	626.10	626.70	0.60					
			635617	626.70	627.50	0.80					

Selwyn Project Diamond Drill Log

Hole Number:
XYC-223

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		up to 70% sulphides. Mineralization: quartz, sphalerite and galena are the major minerals with only minor amounts of pyrite and locally calcite. Sedimentary diagenetic structures are common and well displayed in the facies, such as: lamination, pseudo-beds, calcite nodules & limestone nodules and abundant water escape structures. Most obvious structure in facies is cross-cutting veins containing massive sphalerite and galena with minor pyrite. They range in width from 0.5 to 10mm. - <i>THIN BEDDED CHERTY MUDSTONE FACIES: Consists of rhythmic intercalated laminae of chert, carbonaceous mudstone and minor micrite. This facies contains significant amounts of Zn and Pb sulphides.</i> - <i>CHERTY MUDSTONE FACIES: Consists of a greyish black monotonous siliceous, carbonaceous mudstone. It is most typically found overlying the thin bedded calcareous mudstone facies.</i> - <i>THIN BEDDED CALCAREOUS MUDSTONE FACIES: Consists of laminated carbonaceous mudstone containing 20-40% calcite, 40-55% quartz and 10-20% muscovite. Sulphides occur in laminae. In the XY area it is usually the lowest facies in the section to contain laminated sulphides.</i> - <i>CALCAREOUS MUDSTONE FACIES: Consists of grey to greyish black monotonous, calcareous siliceous carbonaceous mudstone. There are no feathery calcite beds or pyrite-calcite blebs in the facies, making it easily distinguishable from the CCMS.</i> - <i>GRADED LIMESTONE FACIES: Is a laminated argillaceous limestone with intercalated carbonaceous limestone laminae. The main rock type in the facies is laminated limestone with laminae up to 0.1-7mm thick.</i> - <i>LIGHT GREY BASAL LIMESTONE FACIES - LGLS: Consists of laminated argillaceous limestone. In the Anniv area it marks the end of the ACTM. It's not always</i>									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-223

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
present in the stratigraphy.											
- BASAL FACIES: This is a highly contorted and locally foliated carbonaceous mudstone. Unlike the other facies it is not repeated higher in the member. It appears locally to contain the slip zone of a major slump. The facies has only been observed in the YX area. It is 0.1-2m thick. The facies consists of massive carbonaceous siliceous mudstone with lenses and laminae of contorted, slightly carbonaceous chert.											
« 615.90- 618.90 Medium grey siliceous mudstone with thin laminations. Moderate grade. »											
« 618.90- 620.00 Light grey limestone. »											
« 620.00- 621.70 High grade. Light grey siliceous mudstone. »											
« 621.70- 623.60 Barren. Black mudstone. »											
« 623.60- 624.10 Light grey limestone. »											
« 624.10- 625.00 Medium grey, siliceous mudstone with low grades. »											
« 625.00- 627.50 High grade. Light grey, siliceous mudstone. »											
627.50	648.40	CCMS	635618	627.50	628.30	0.80					
CCMS – Calcareous Mudstone			635619	628.30	629.00	0.70					
			635620	629.00	629.00	0.00					
Massive, calcareous, carbonaceous, dark grey mudstone. Most of the member is massive, but rare poorly defined bedding and pyrite-calcite micro-concretions are present. Most diagnostic structures are feathery calcite beds (=thin calcite-cemented concretions, many of them contain pyrite cores) and calcite pseudo-beds (= fibrous calcite vein parallel to bedding).											
« lm ca 5.00-10.00mm », « nodules py -3.00% 2.00-20.00mm »,											
Black, carbon-rich, siliceous mudstone.											



Hole Number:
XYC-223

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

Printed on: 2011/06/13

Diamond Drill Log

Comprehensive Report for Hole:

XYC-222

Hole No.: XYC-222	Depth: 147.20 m	Horizontal Length: 0.00 m	Project: 1710
Location Data:			
Property:	Selywn Project	Claim Name:	X 11
Mining District:	Selwyn Basin	Grant Number:	Y 64536
Province/Territory:	Yukon		
UTM Co-Ordinates & Altitude of Drill Hole Collar:			
UTM Easting:	488514.00 m	True Azimuth:	210.0 °
UTM Northing:	6926438.00 m	Hole Angle:	-65.0 °
Elevation (m):	1564.00 m	NTS Name:	Placer Creek
		NTS Number:	105I06
Grid Co-Ordinates of Drill Hole Collar:			
Grid Easting (m):	0.00 m	Grid Name:	HP 06
Grid Northing (m):	0.00 m	Grid Type:	100m
Grid Azimuth:	270.0 °		
Dimond Drilling Contract:			
Drilled By:	CY-02	Date Drilling Start:	10/03/2010
		Date Finish:	10/09/2010
Diamond Drill Core:			
Logged By:	Kate Cameron	Date Logging Start:	10/15/2010
		Date Finish:	10/17/2010
Legend for Core Logging Codes: PAX			
Core Size:	NQ/NQ3	Cemented:	Yes
Casing Depth:	9.80 m	Casing Pulled:	Yes
Water Depth:	0.00 m	Overburden Depth:	9.80 m
Level:		Section:	
		Drift:	

Selywn Project

Diamond Drill Log

Survey Data for Hole

XYC-222

Hole Comments:

Mon, Oct 04 --- Yesterday Ken started pulling the drill to the setup (target #20). While they were pulling the drill, it became clear the drill shack was too wide to get past a certain spot. They had to remove one of the walls in order to get past it. There is no night shift yet on this drill.

=====

Tue, Oct 05 --- Start drilling today at target #20.

=====

Wed, Oct 06 --- Drilled 9.1m of casing, at a total depth of 14m, core is at XY, no geologist has seen core yet.

=====

Thu, Oct 07 --- At a total depth of 50m, switching to NQ3, in HW rocks (FLMD, it was dark), blocky ground.

=====

Fri, Oct 08 --- At a total depth of 107m in ACTM (15%Zn), still blocky, poor recovery around 95m.

=====

Sat, Oct 09 --- got shut down this morning at 147m in CCMS, feathery calcite beds and pyrite pseudobeds. Fault from 116- 127m. Out of ACTM at 118m. Going back down hole to test and cement, then ready to move today.

<i>Depth</i>	<i>Dip</i>	<i>Azimuth</i>
0.00	-65.0	210.0
50.00	-64.0	211.0
104.00	-62.0	212.1
149.00	-61.1	214.6

Selwyn Project Diamond Drill Log

Hole Number:
XYC-222

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
0.00	9.80	OVBR									
9.80	82.60	USMS	633301	25.90	27.60	1.70	0.01	0.32	1.00	10.00	0.03
<i>USMS – Upper Siliceous Mudstone</i> <i>Consists of interlaminated dark grey to black mudstone and light to medium grey chert. Regionally, a 1m thick graptolite zone occurs 15m below the top of the upper unit, this is usable as a horizon. The USMS is divided into 3 units. The Lower Unit contains abundant limestone concretions and Galena and sphalerite micro-concretions occur locally near the base of this unit. « gra , lm chrt -20.00% », « cg xtl sph crns ca 5.00-20.00cm », « bed chrt 10.00-15.00% »,</i> <i>Pretty standard stuff. Black carbonaceous mudstone. Wormy, greyish chert bands with pyrite disseminations. Some calcite veins, stringy-spiderly. Competent rock. Bedding at sub-perpendicular TCA to very deformed --> seen in banding and pyrite disseminated layers.</i> <i>« 23.10- 25.90 Lost of mechanical breakage as well. Breaks are blocky, low grade slate, barely layered mdst. FLT »« brkn core 20%»« flt bx 79%»« flt gg 1%»</i> <i>« 25.90- 27.60 Si (carb) mdst with abundant wormy grey chert bands. Minor MX --> Zn 0.60% according to Niton »</i> <i>« 27.60- 28.20 Med. grey lmst with very fine spiderly ca stringers. Lmst is coarse in some spots, almost crystalline. Niton reads 0% »</i> <i>« 28.20- 29.60 Plain USMS, no MX visible or indicated by Niton »</i> <i>« 29.60- 30.60 MX zone. Brownish lt-med grey. Fine lams disrupted by frequent micro-faulting. Lam contain ga and sph. Flts contain ga, ca and py. »« Ga also occurs as larger blebs asso. with a wider ca vein. Original lams are quite distorted, but could have been sub perpendicular to 50 degrees tca. »</i>			633302	27.60	28.20	0.60	0.01	0.01	1.00	5.00	2.00
			633303	28.20	29.60	1.40	0.01	0.02	1.00	5.00	0.50
			633304	29.60	30.60	1.00	6.08	13.23	14.00	670.00	0.46
			633305	30.60	32.00	1.40	0.47	0.34	1.00	10.00	1.38
			633306	78.60	80.00	1.40	0.02	0.09	1.00	5.00	0.22
			633307	80.00	80.90	0.90	0.16	0.30	1.00	5.00	0.53
			633308	80.90	82.60	1.70	0.03	0.21	1.00	5.00	0.14

Selwyn Project Diamond Drill Log

Hole Number:
XYC-222

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
« 30.60- 82.60 USMS as normal- abundant ca stringers and chert bands parallel to each other. S0 tca 50°»« Local, small (2-25cm) sections of coarse lmst without radial lams --> do have weak internal lams and sharp boundaries. Graphitic »											
« 33.30- 47.80 Slicken slides present. Ca and gypsum are ground up as part of the gouge. »« brkn core 30%»« flt bx 50%»« flt gg 20%»											
« 47.80- 78.60 Well broken zone. Intact sections are lmst. Fractures are parallel and dominantly 45-55 degrees tca. Slicken slides present BRKN »											
« 80.90- 82.60 Change of unit and core lost. Dont know if USMS was cut short because no upper contact for reference. »« brkn core 5%»« flt bx 5%»« flt gg 90%»											
82.60	135.80	ACTM	633309	82.60	83.20	0.60	0.84	4.74	3.00	200.00	0.18
ACTM – Active Member			633310	83.20	83.60	0.40	0.06	0.23	1.00	5.00	0.26
			633311	83.20	83.60	0.40	0.05	0.36	1.00	10.00	0.14
			633312	83.60	85.00	1.40	1.05	8.77	4.00	270.00	0.12
			633313	85.00	86.40	1.40	2.01	16.44	5.00	680.00	0.12
			633314	86.40	86.70	0.30	2.55	16.81	3.00	920.00	0.15
			633315	86.70	87.50	0.80	2.73	7.19	3.00	300.00	0.38
			633316	87.50	89.00	1.50	1.07	5.02	1.00	120.00	0.21
			633317	89.00	89.40	0.40	0.97	5.22	1.00	120.00	0.19
			633318	89.40	89.70	0.30	0.16	0.51	1.00	10.00	0.31
			633319	89.70	90.60	0.90	0.06	0.62	1.00	20.00	0.10
			633320	90.60	90.60	0.00	0.01	0.01	1.00	5.00	2.00
			633321	90.60	94.90	4.30	1.27	3.87	1.00	110.00	0.33
			633322	94.90	95.50	0.60	0.20	1.21	1.00	30.00	0.17
			633323	95.50	97.00	1.50	0.79	1.52	1.00	40.00	0.52
			633324	97.00	99.00	2.00	0.43	2.38	1.00	70.00	0.18
			633325	99.00	99.70	0.70	1.40	5.44	1.00	160.00	0.26
			633326	99.70	101.00	1.30	0.14	0.32	1.00	10.00	0.44
			633327	101.00	101.90	0.90	1.14	2.74	1.00	80.00	0.42

Selwyn Project Diamond Drill Log

Hole Number:
XYC-222

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
diagenetic structures are common and well displayed in the facies, such as: lamination, pseudo-beds, calcite nodules & limestone nodules and abundant water escape structures. Most obvious structure in facies is cross-cutting veins containing massive sphalerite and galena with minor pyrite. They range in width from 0.5 to 10mm. - THIN BEDDED CHERTY MUDSTONE FACIES: Consists of rhythmic intercalated laminae of chert, carbonaceous mudstone and minor micrite. This facies contains significant amounts of Zn and Pb sulphides. - CHERTY MUDSTONE FACIES: Consists of a greyish black monotonous siliceous, carbonaceous mudstone. It is most typically found overlying the thin bedded calcareous mudstone facies. - THIN BEDDED CALCAREOUS MUDSTONE FACIES: Consists of laminated carbonaceous mudstone containing 20-40% calcite, 40-55% quartz and 10-20% muscovite. Sulphides occur in laminae. In the XY area it is usually the lowest facies in the section to contain laminated sulphides. - CALCAREOUS MUDSTONE FACIES: Consists of grey to greyish black monotonous, calcareous siliceous carbonaceous mudstone. There are no feathery calcite beds or pyrite-calcite blebs in the facies, making it easily distinguishable from the CCMS. - GRADED LIMESTONE FACIES: Is a laminated argillaceous limestone with intercalated carbonaceous limestone laminae. The main rock type in the facies is laminated limestone with laminae up to 0.1-7mm thick. - LIGHT GREY BASAL LIMESTONE FACIES - LGLS: Consists of laminated argillaceous limestone. In the Anniv area it marks the end of the ACTM. It's not always present in the stratigraphy. - BASAL FACIES: This is a highly contorted and locally foliated carbonaceous			633328	101.90	103.40	1.50	0.01	0.03	1.00	5.00	0.33
			633329	103.40	103.60	0.20	0.31	0.48	1.00	10.00	0.65
			633330	103.60	103.60	0.00	0.93	1.31	225.00	90.00	0.71
			633331	103.60	103.90	0.30	2.46	11.63	3.00	390.00	0.21
			633332	103.90	104.20	0.30	2.23	9.93	2.00	330.00	0.22
			633333	104.20	105.40	1.20	2.80	7.48	2.00	260.00	0.37
			633334	105.40	106.40	1.00	5.03	14.95	4.00	430.00	0.34
			633335	106.40	107.10	0.70	8.27	22.24	4.00	910.00	0.37
			633336	107.10	108.30	1.20	9.29	22.07	6.00	760.00	0.42
			633337	108.30	109.00	0.70	3.11	8.37	2.00	320.00	0.37
			633338	109.00	110.00	1.00	6.19	22.91	6.00	720.00	0.27
			633339	110.00	111.50	1.50	4.08	19.92	4.00	530.00	0.20
			633340	111.50	112.50	1.00	4.83	16.57	4.00	390.00	0.29
			633341	111.50	112.50	1.00	5.11	17.11	5.00	390.00	0.30
			633342	112.50	112.60	0.10	4.77	13.56	5.00	360.00	0.35
			633343	112.60	114.10	1.50	1.92	13.02	3.00	320.00	0.15
			633344	114.10	115.60	1.50	0.80	4.23	1.00	100.00	0.19
			633345	115.60	118.40	2.80	7.59	7.10	5.00	210.00	1.07
			633346	118.40	120.60	2.20	0.05	0.73	1.00	20.00	0.07
			633347	120.60	122.00	1.40	0.04	0.19	1.00	5.00	0.21
			633348	122.00	125.00	3.00	0.09	0.72	1.00	20.00	0.13
			633349	125.00	127.40	2.40	0.11	0.34	1.00	5.00	0.32
			633350	127.40	127.40	0.00	0.01	0.01	1.00	5.00	2.00
			633351	127.40	128.00	0.60	0.22	0.25	1.00	5.00	0.88
			633352	128.00	129.50	1.50	0.30	1.43	3.00	40.00	0.21
			633353	129.50	131.00	1.50	0.16	1.24	1.00	40.00	0.13
			633354	131.00	132.50	1.50	0.45	1.19	3.00	30.00	0.38
			633355	132.50	134.00	1.50	2.05	1.99	8.00	50.00	1.03
			633356	134.00	135.10	1.10	0.18	1.44	1.00	40.00	0.13
			633357	135.10	135.80	0.70	0.01	0.01	1.00	5.00	2.00

Selwyn Project Diamond Drill Log

Hole Number:
XYC-222

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		mudstone. Unlike the other facies it is not repeated higher in the member. It appears locally to contain the slip zone of a major slump. The facies has only been observed in the YX area. It is 0.1-2m thick. The facies consists of massive carbonaceous siliceous mudstone with lenses and laminae of contorted, slightly carbonaceous chert. Active member begins right after the fault. Standard low-medium grade with fine laminae of sphalerite and some laminae containing galena. Matrix is black mudstone--> can be carbonaceous and/or calcareous. Sections of coarse, interally laminated limestone do not look like concretions --> clast or seperate deposition event? Shows are internal faulting and angle of laminae is changing constantly. Pyrite, especially associated with calcite veins/blebs is common. Variable calcite veins are frequent. « 82.60- 83.20 Calc mdst with some spa lams. Dk grey with brownish tine to almost black. Pb 3.81%, Zn 4.07% » « 83.20- 83.60 Coarse lt grey lmst with muddy lams and calcite veins. Pb 0.4%, Zn 0.56% » « 83.60- 86.40 Blk Si-rich mdst w/ lots of py and other mx. Pb 2.43%, Zn 8.32%. Sph appears fine gained in distorted lams. Ga is same but much less visible. » « 86.40- 86.70 Lt-med grey highly Si mdst w/ py and ca veins. Sph and ga in laminae. Pb 3.8%, Zn 7.73% » « 86.70- 87.40 Med-dk grey mdst with sph and ga in laminae. Pb 9.63%, Zn 7.46 % » « 87.40- 87.50 F.g. med-lt grey lmst with planar ca veins. Included with sample above by mistake. »									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-222

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		« 87.50- 89.00 Dk grey-blk Si mdst with ca veins. All within fault. Pb 1.67%, Zn 7.97% » « FLT »« brkn core 40%»« flt bx 50%»« flt gg 10%» « 89.00- 89.40 Med grey Si laminated mdst with some lmst concretions or fragments. Shpalerite in laminae. Pb 0% Zn 0.33% » « 89.40- 89.70 Med-coarse grained lmst. Light grey. Slightly silty or muddy. Laminae are parallel with laminae in mdst above and below. » « 89.70- 95.50 Si mdst with some calc and carb sections. Pyrite is the only visible MX. Pb 0.13% Zn 0% » « 90.60- 94.9 Some turning in the drill broke this pre-existing broken area up further, making it hard to say exactly how much bx was whole core in situ. Slick n slides present. FLT »« brk pc 15%»« bx 65%»« gg 20%» « 95.50- 99.00 Light grey lmst with very thing plannar, parallel calc veins (and a few randomly oriented ones). Laminae are roughly parallel to others in upper ACTM (55 deg) TCA. No vis MX. Pb 0.64% Zn 0.84% » « 98.10- 99.00 FLT » « Fault. Appears to be about 1 m of core loss. Mostly blk, carb gouge. « brk pc »« bx 10%»« gg 90%»» « 99.00- 99.70 Dk grey to blk calc mdst. Warped laminae with small amount of sphalerite. Pb 0.14%, Zn 4.68%. » « 99.70- 101.00 Fine grained lmst with calc veins almost obliterating it. Pb 0%, Zn 0.40%. » « 101.00- 101.90 Blk highly siliceous mdst with sparse, irregular, thin calc veins. Monotonous. No vis MX. Pb 0.20%, Zn 0.57%. » « 101.30- 101.40 Fault with core loss, pure breccia. FLT »« bx 100%»									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-222

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		« 101.90- 102.00 Fault with core loss. Pure breccia. FLT »« bx 100%»									
		« 101.90- 103.40 Coarse med-grey lmst with planar laminae. No MX visible or detectible with Niton. »									
		« 103.40- 103.60 Blk highly siliceous mdst with sparse, irregular, thin calc veins. Monotonous. No MX visible or detected with Niton. »									
		« 103.60- 103.70 Fault. Core lost. Pure breccia. »« bx 100%»									
		« 103.60- 103.90 Closely spaced bands of laminated dk grey mdst and light grey coarse lmst. Pb 1.98%, Zn 5.13%. »									
		« 103.90- 104.20 Blk Si mdst grading to lt grey Si mdst with MX in laminae. Pyrite is abundant. Small amount of sphalerite and galena visible. Pb 3.72%, Zn 5.9%. »									
		« 104.20- 105.40 Lmst with thin-planar as well as thick-irregular calcite veins. No vis MX. Pb 0%, Zn 1.11%. »									
		« 104.40- 106.50 Fault that may be a small set of faults based on multiple discrete sections of gouge FLT »									
		« 105.40- 108.30 Increase Si med grey mdst. Dense, competent rock. Thick distorted laminae. sph 10%; ga 15%. »									
		« 108.30- 110.00 Si mdst and strongly calcareous lmst. Thin, planar laminae. Pb 5 - 17%; Zn 6- 23% »									
		« 110.00- 118.40 Si med grey mdst. Distorted light and dark mud laminae. Pb 0.95-5.76%; Zn 7.52-11.35% »									
		« 115.60- 127.40 Gouge is frequently 're-constituted' but falls apart very easily. Carb. sections are the most ground up. Calcite veins up to 30cm are somewhat intact. »« flt gg 50%»« flt bx 30%»« brco 20%»									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-222

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
« 118.40- 127.40 Black calc and carb mdst with small intervals (10 to 20cm) of lmst or calc veins. Mostly re-constituted gouge. » « 127.40- 128.10 Black Si mdst with frequent microfaulted calcite veins. Pyrite associated with thicker calcite veins. Pb 0.16%; Zn 0.21% » « 128.10- 135.10 Calc carb dark grey-black mdst. Micro faulted calcite veins. Disseminated py in discreet bands (sedex feature) Pb 0.32%; Zn 0.71% » « 133.50- 133.80 Slicken Slide surfaces. Not much loss of core FLT »« flt gg 5%»« flt bx 5%»« brco 90%» « 134.20- 134.30 Unknown length because there are several faults between blocks where core appears to be lost. FLT »« flt gg 50%»« flt bx 50%» « 134.90- 135.10 As last FLT »« flt gg 20%»« flt bx 30%»« brco 50%» « 135.10- 135.80 Fine grained lmst with fine laminae and thin calcite veins. Light grey Basal lmst? End of active member. » « 135.80- 137.50 Exact end depth is not known because there is another fault with loss of core before next block FLT »« flt gg 40%»« flt bx 60%»											
135.80	147.20	CCMS	633358	135.80	139.50	3.70	0.02	0.01	1.00	5.00	2.00
CCMS – Calcareous Mudstone			633359	139.50	141.00	1.50	0.01	0.03	1.00	5.00	0.33
			633360	141.00	141.00	0.00	1.41	4.31	26.00	270.00	0.33
Massive, calcareous, carbonaceous, dark grey mudstone. Most of the member is massive, but rare poorly defined bedding and pyrite-calcite micro-concretions are present. Most diagnostic structures are feathery calcite beds (=thin calcite-cemented concretions, many of them contain pyrite cores) and calcite pseudo-beds (= fibrous calcite vein parallel to bedding). « lm ca 5.00-10.00mm », « nodules py -3.00% 2.00-20.00mm »,											

Selwyn Project Diamond Drill Log

Hole Number:
XYC-222

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		Black, monotonous. Infrequent calcite veins, wispy ro a few mm. Siliceous. Non caclareous. Occassional bands of disseminated pyrite. « 138.00- 139.50 Exact start depth unknown because of overlying fault bewteen start and a block. FLT »« flt gg 60%»« flt bx 30%»« brco 10%»									
147.20	147.20	EOH									

Diamond Drill Log

Comprehensive Report for Hole:

XYC-221

Hole No.: XYC-221	Depth: 194.00 m	Horizontal Length: 0.00 m	Project: 1710
Location Data:			
Property:	Selwyn Project	Claim Name:	X 15
Mining District:	Selwyn Basin	Grant Number:	Y 64540
Province/Territory:	Yukon		
UTM Co-Ordinates & Altitude of Drill Hole Collar:			
UTM Easting:	489137.00 m	True Azimuth:	210.0 °
UTM Northing:	6926297.00 m	Hole Angle:	-80.0 °
Elevation (m):	1634.00 m	NTS Name:	Placer Creek
		UTM Datum:	NAD 83
		UTM Grid Zone:	9
		NTS Number:	105L06
Grid Co-Ordinates of Drill Hole Collar:			
Grid Easting (m):	0.00 m	Grid Name:	HP 06
Grid Northing (m):	0.00 m	Grid Type:	100m
Grid Azimuth:	270.0 °		
Dimond Drilling Contract:			
Drilled By:	CY-01	Date Drilling Start:	10/03/2010
		Date Finish:	10/07/2010
Diamond Drill Core:			
Logged By:	Kate Cameron / Graham	Date Logging Start:	10/28/2010
		Date Finish:	11/06/2010
Legend for Core Logging Codes: PAX			
Core Size:	NQ	Cemented:	Yes
Casing Depth:	9.90 m	Casing Pulled:	Yes
Water Depth:	0.00 m	Overburden Depth:	9.90 m
Level:	Section:	Drift:	

Selwyn Project

Diamond Drill Log

Survey Data for Hole

XYC-221

Hole Comments:

Fri, Oct 01 --- XYC-209 got shut down yesterday late morning in CCMS. After pulling the rods, taking flexit tests and cementing from EOH to a depth of 520m, they moved the drill to target #34. Matt and Graham were there to line up the drill, but due to unexpected roadwork in order to get the drill to the setup and nightfall, it was not possible to finish the move yesterday evening.

=====

Sat, Oct 02 --- Right now in BSSM at a total depth of 78m. About 15m of casing was put in.

=====

Sun, Oct 03 --- Still in BSSM at a total depth of 111m. They drilled 33m in the past 24hrs.

=====

Mon, Oct 04 ---Still in BSSM at a total depth of 177m. Bioturbations are present locally.

=====

Tue, Oct 05 --- In FLMD at a depth of 213m

=====

Wed, Oct 06 ---Still in FLMD at depth of 239m. Troubles at drill last night -- rubbers on the back-end could not go through landing rig, dropped core as a result.

=====

Thu, Oct 07 --- Still in FLMD at depth of 261m.

=====

Fri, Oct 08 --- Total depth of 304.8m in USMS

<i>Depth</i>	<i>Dip</i>	<i>Azimuth</i>
0.00	-80.0	210.0
50.00	-78.7	215.2
101.00	-76.7	210.4
152.00	-76.4	211.2
197.00	-75.6	212.4

Selwyn Project Diamond Drill Log

Hole Number:
XYC-221

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
0.00	9.90	OVBR									
9.90	80.30	FLMD									
FLMD – Flaggy Mudstone Formation											
Dark grey mudstone in the upper portions of the unit grading into light grey mudstone to siltstone. Contains abundant wispy bioturbation which ranges from randomly-oriented at the top of the unit to bedding-parallel throughout the majority of the unit. Darker upper section has a strong fetid odour along broken surfaces. « btrb 0.10-2.00cm », « cg xtl crns ca 1.00-5.00% 5.00-150.00cm », « crns py 1.00-5.00% 0.10-0.50mm »											
« 9.90- 18.90 Surface broken zone. »											
< @ 19.30 S0 defined by bioturbation. S0 tca 35° >											
< @ 30.00 S0 defined by bioturbation. S0 tca 45° >											
< @ 44.80 S0 defined by bioturbation. S0 tca 25° >											
< @ 61.00 S0 defined by bioturbation. S0 tca 40° >											
< @ 65.60 S0 defined by bioturbation. S0 tca 40° >											
< @ 69.20 S0 defined by bioturbation. S0 tca 30° >											
« 68.60- 69.00 Flt »« Flt gg 70%»« Flt bx 30%»											
« 70.00- 80.30 Mangled bedding. Bioturbation at random orientations. »											
80.30	148.50	USMS	635051	145.00	145.80	0.80	0.01	0.11	1.00	5.00	0.09
USMS – Upper Siliceous Mudstone			635052	145.80	147.20	1.40	0.12	0.61	1.00	20.00	0.20
			635053	147.20	148.50	1.30	0.04	0.39	1.00	10.00	0.10
Consists of interlaminated dark grey to black mudstone and light to medium grey chert. Regionally, a 1m thick graptolite zone occurs 15m below the top of the upper unit, this is usable as a horizon. The USMS is divided into 3 units. The Lower Unit contains abundant limestone concretions and Galena and sphalerite micro-concretions occur locally near the base of this unit. « gra , lm chrt -20.00% », « cg xtl sph crns ca 5.00-20.00cm », « bed chrt 10.00-15.00% »											

Selwyn Project Diamond Drill Log

Hole Number:
XYC-221

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		« 80.30- 92.00 Some sections are flaggy, but USMS material. Flt »« Flt gg 50%»« Flt bx 30%»« Brco 10%»									
		« 92.00- 117.10 Typical USMS variable degrees of banding from less than 5% to greater than 90%, chert, pyrite, calcic, carbonaceous bands. Laminated limestone clasts (2-15cm wide). Framboildal pyrite with calcic rims (1-7mm). »									
		< @ 95.30 S0 defined by chert band. S0 tca 49° > < @ 101.20 S0 defined by chert band. S0 tca 82° > < @ 104.70 S0 defined by pyritic band. S0 tca 60° > < @ 114.50 S0 defined by calcite band. S0 tca 50° >									
		« 117.10- 126.80 Mylonitic fault breccia zone with reconstituted breccia fragments. Increases in qt-cal veins and compression of S0. Abundant slippage in plane-parallel fashion. »									
		< @ 117.80 S0 defined by plane-parallel fracture. S0 tca 37° >									
		« 126.80- 140.00 Faulted zone, blocky ground. Faulting is chaotic and crosses the major tectonic fabric. Limestone clasts resist deformation. Flt »« Flt gg 10%»« Flt bx 10%»« Brco 80%»									
		« 140.00- 142.00 Typical USMS »									
		« 142.00- 142.80 Laminated and graded limestone. »									
		« 142.80- 147.10 Typical USMS »									
		« 147.10- 148.50 Heavily fractured and veined with recrystallized qt-cal, primary features are obliterated by vein swarms which brecciate and re-cement the mudstone. »									
148.50	160.20	ACTM	635054	148.50	149.70	1.20	11.93	10.45	1.00	610.00	1.14
		ACTM – Active Member	635055	149.70	150.60	0.90	16.68	20.40	3.00	1150.00	0.82

Selwyn Project Diamond Drill Log

Hole Number:
XYC-221

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
The ACTM consists of a repetitive, possibly rhythmic, sequence of intercalated carbonaceous mudstone, cherty mudstone, chert and limestone and locally contains economically significant Zn and Pb sulphides (see bold marked facies), mainly in its sections with well developed lamination. Because of its heterogeneity, the member is distinctive and easily identified. ===== The ACTM has 8 different facies: ===== - GREY CHERT FACIES: Consists of laminated medium light grey to medium dark grey chert. Mineralization: 95-99% quartz and up to 5% secondary calcite. - WHITISH GREY ZN-PB MUDSTONE FACIES: Is a laminated cherty rock containing up to 70% sulphides. Mineralization: quartz, sphalerite and galena are the major minerals with only minor amounts of pyrite and locally calcite. Sedimentary diagenetic structures are common and well displayed in the facies, such as: lamination, pseudo-beds, calcite nodules & limestone nodules and abundant water escape structures. Most obvious structure in facies is cross-cutting veins containing massive sphalerite and galena with minor pyrite. They range in width from 0.5 to 10mm. - THIN BEDDED CHERTY MUDSTONE FACIES: Consists of rhythmic intercalated laminae of chert, carbonaceous mudstone and minor micrite. This facies contains significant amounts of Zn and Pb sulphides. - CHERTY MUDSTONE FACIES: Consists of a greyish black monotonous siliceous, carbonaceous mudstone. It is most typically found overlying the thin bedded calcareous mudstone facies. - THIN BEDDED CALCAREOUS MUDSTONE FACIES: Consists of laminated carbonaceous mudstone containing 20-40% calcite, 40-55% quartz and 10-20% muscovite.			635056	150.60	151.90	1.30	26.89	27.07	10.00	1530.00	0.99
			635057	151.90	153.30	1.40	24.60	24.47	9.00	1570.00	1.01
			635058	153.30	154.00	0.70	24.84	26.89	11.00	1550.00	0.92
			635059	154.00	154.90	0.90	7.41	12.67	3.00	600.00	0.58
			635060	154.90	155.70	0.80	6.21	9.87	3.00	470.00	0.63
			635061	154.90	155.70	0.80	5.02	8.04	3.00	380.00	0.62
			635062	155.70	156.40	0.70	0.13	0.19	1.00	5.00	0.68
			635063	156.40	157.30	0.90	0.39	0.39	1.00	20.00	1.00
			635064	157.30	157.80	0.50	0.05	0.42	1.00	10.00	0.12
			635065	157.80	158.30	0.50	0.17	1.09	1.00	30.00	0.16
			635066	158.30	159.00	0.70	0.25	0.56	1.00	20.00	0.45
			635067	159.00	159.60	0.60	0.57	0.63	1.00	20.00	0.90
			635068	159.60	160.20	0.60	0.46	1.82	1.00	50.00	0.25

Selwyn Project Diamond Drill Log

Hole Number:
XYC-221

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		Sulphides occur in laminae. In the XY area it is usually the lowest facies in the section to contain laminated sulphides. - CALCAREOUS MUDSTONE FACIES: Consists of grey to greyish black monotonous, calcareous siliceous carbonaceous mudstone. There are no feathery calcite beds or pyrite-calcite blebs in the facies, making it easily distinguishable from the CCMS. - GRADED LIMESTONE FACIES: Is a laminated argillaceous limestone with intercalated carbonaceous limestone laminae. The main rock type in the facies is laminated limestone with laminae up to 0.1-7mm thick. - LIGHT GREY BASAL LIMESTONE FACIES - LGLS: Consists of laminated argillaceous limestone. In the Anniv area it marks the end of the ACTM. It's not always present in the stratigraphy. - BASAL FACIES: This is a highly contorted and locally foliated carbonaceous mudstone. Unlike the other facies it is not repeated higher in the member. It appears locally to contain the slip zone of a major slump. The facies has only been observed in the YX area. It is 0.1-2m thick. The facies consists of massive carbonaceous siliceous mudstone with lenses and laminae of contorted, slightly carbonaceous chert. « 148.50- 149.70 Light grey laminated sphalerite and galena in breccia pieces, minor intercalated mudstone. FLT »« Flt gg 5%»« Flt bx 80%»« Brco 15%» « 149.70- 153.30 Very high grade laminated galena ~30% and sphalerite ~25%. Many patches of broken core and breccia. Minor calcite blebs and veins are often associated with pyrite. Small sections of coarse limestone, also rare limestone clasts. » « 153.30- 154.00 Same lithology as previous, in addition there is more mud component (galena ~30%, sphalerite ~20%) FLT »« Flt gg 10%»« Flt bx 70%»«									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-221

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
Brco 30%» « 154.00- 154.90 Same lithology as previous, with slightly less galena and sphalerite; 20 and 15% respectively. » « 154.90- 157.30 Dark grey carbonaceous mudstone, weakly laminated and distorted by rounded limestone clasts. Abundant pressure dissolution seams and stylolites and swarms. Pseudotachylite is well developed through the interval. » « 157.30- 158.30 Laminated dark grey mudstone. Laminae are regular, graded, ~3-10mm thick. Lighter grey laminae base grades into darker grey, fine grained mud. Small intervals of 10-20cm are enriched with fine grained sphalerite and galena. Layers are brownish and lighter colour when sphalerite enrichment occurs. » « 158.30- 159.00 Laminated mud-rich fine grained limestone. Cross-laminated structure. Veined with calcite and qt 2-4mm, typically <1mm though. No visible mineralization. » « 159.00- 159.60 FLT »« Flt gg 20%»« Flt bx 70%»« Brco 10%» « 159.60- 160.20 Basal limestone. Light grey laminated limestone with mudstone incorporated in amounts <5cm thick. Minor pyrite occurs with qt-cal. Contact at the base of Active Member basal limestone with ccms occurs over ten cm and appears to be depositional, interbedded limestone and dark-grey-black carbonaceous mudstone. Marked with an increase in calcite and quartz. »											
160.20	194.00	CCMS	635069	160.20	160.80	0.60	1.68	0.78	5.00	20.00	2.15
CCMS – Calcareous Mudstone			635070	160.80	160.80	0.00	0.01	0.01	1.00	5.00	2.00
Massive, calcareous, carbonaceous, dark grey mudstone. Most of the member is massive, but rare poorly defined bedding and pyrite-calcite micro-concretions are present. Most diagnostic structures are feathery calcite beds (=thin calcite-cemented concretions, many of them contain pyrite cores) and calcite			635071	160.80	161.80	1.00	0.61	0.42	5.00	20.00	1.45
			635072	161.80	162.10	0.30	0.03	0.01	1.00	5.00	6.00
			635073	162.10	162.50	0.40	0.01	0.01	1.00	5.00	2.00
			635074	162.50	162.80	0.30	0.04	0.08	2.00	5.00	0.50

Selwyn Project Diamond Drill Log

Hole Number:
XYC-221

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		<i>pseudo-beds (= fibrous calcite vein parallel to bedding).</i> « lm ca 5.00-10.00mm », « nodules py -3.00% 2.00-20.00mm » « 160.20- 162.80 Dark-grey to black weakly calcareous mudstone, pseudo-beds of specular calcite and pyrite. Calcite-qt remineralized stylolites. Faint distorted laminae occur as various shades of dark grey 2-8mm thick with periodic massive limestone laminae 2-4cm thick. » « 162.80- 174.90 Dark grey to black, very typical CCMS, thin wispy calcite bands, pyrite pseudo laminae, framboidal pyrite with calcite/quartz veins. Minor zones of breccia faulting 3-7cm thick. Spotted calcite helps define a rough S0. » « 174.90- 178.50 Poor recovery FLT »« Flt gg 2%»« Flt bx 70%»« Brco 28%» « 178.50- 194.00 As described, typical CCMS. » < @ 165.80 S0 defined by cherty, calcic laminae. S0 tca 35° > < @ 168.50 S0 defined by pyritic laminae. S0 tca 75° > < @ 182.00 S0 defined by wispy calcite. S0 tca 85° > < @ 186.40 S0 defined by wispy calcite. S0 tca 72° >									
194.00	194.00	EOH									

Diamond Drill Log

Comprehensive Report for Hole:

XYC-220

Hole No.: XYC-220	Depth: 281.50 m	Horizontal Length: 0.00 m	Project: 1710
Location Data:			
Property:	Selwyn Project	Claim Name:	X46
Mining District:	Selwyn Basin	Grant Number:	Y 64679
Province/Territory:	Yukon		
UTM Co-Ordinates & Altitude of Drill Hole Collar:			
UTM Easting:	487502.60 m	True Azimuth:	40.0 °
UTM Northing:	6927240.23 m	Hole Angle:	-72.0 °
Elevation (m):	1486.18 m	NTS Name:	Placer Creek
		NTS Number:	105L06
Grid Co-Ordinates of Drill Hole Collar:			
Grid Easting (m):	0.00 m	Grid Name:	HP 06
Grid Northing (m):	0.00 m	Grid Type:	100m
Grid Azimuth:	100.0 °		
Dimond Drilling Contract:			
Drilled By:	NL-02	Date Drilling Start:	10/2/2010
		Date Finish:	10/7/2010
Diamond Drill Core:			
Logged By:	Kate Cameron / Gabe Xue	Date Logging Start:	10/28/2010
		Date Finish:	01/11/2011
Legend for Core Logging Codes: PAX			
Core Size:	NQ	Cemented:	Yes
Casing Depth:	13.40 m	Casing Pulled:	Yes
Water Depth:	0.00 m	Overburden Depth:	13.40 m
Level:			
Section:			
Drift:			

Selwyn Project

Diamond Drill Log

Survey Data for Hole

XYC-220

Hole Comments:

Sun, Oct 03 --- The hole collared probably in FLMD, or possibly in a FLMD looking stretch in BSSM. The core is light grey and shows bioturbations. The overburden is approximately 13.5m thick.

=====

Mon, Oct 04 ---At a total depth of 152m. The hole was in FLMD up to a depth of 140.5m, then a fault was hit.

=====

Tue, Oct 05 --- At a total depth of 222.5m. Below the fault occurs discontinuous mineralized sections up to 50cm long grading up to 4% combined Pb, Zn starting at 189m, believed to be start of ACTM. ACTM still being drilled at 222.5m with localized high grade Pb, Zn and abundant faulting.

=====

Wed, Oct 06 ---At a total depth of 266.7m. Out of active member at 253.5m, into zone of faulting and brecciated CCMS. Tough night at the drill -- dropped drill rod down hole while changing bit.

=====

Thu, Oct 07 --- "XYC-220 was plotted, and because the dip of hole is not flattening as planned the final depth will increase from 350m's to 400. We should hit a second lens according to current XY West Model" At a total depth of 278.5m in CCMS.

=====

Fri, Oct 08 --- Rods are stuck in XYC 220 (target #48), unable to recover. The NQ string is to be left in the hole with the casing capped. Drill to adjust for target #47 and attempt to intersect second ACTM lens. If this hole hits the second ACTM lens we will return to XYC-220 and reduce to BQ, if it doesnt hit the second lens we'll go back to XYC-220 and cut the rods.

Note:

Cut the rods twice but could not get them loose. We pay for 50 rods and core barrel. No Limit to pay for 42 rods.

<i>Depth</i>	<i>Dip</i>	<i>Azimuth</i>
0.00	-72.0	40.0
53.00	-73.1	39.7
107.00	-72.4	39.4
152.50	-73.1	36.7
200.00	-73.1	41.2
251.50	-72.7	37.6

Selwyn Project Diamond Drill Log

Hole Number:
XYC-220

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
0.00	13.40	OVBR									
13.40	140.90	FLMD									
<i>FLMD – Flaggy Mudstone Formation</i>											
<i>Dark grey mudstone in the upper portions of the unit grading into light grey mudstone to siltstone. Contains abundant wispy bioturbation which ranges from randomly-oriented at the top of the unit to bedding-parallel throughout the majority of the unit. Darker upper section has a strong fetid odour along broken surfaces. « btrb 0.10-2.00cm », « cg xtl crns ca 1.00-5.00% 5.00-150.00cm », « crns py 1.00-5.00% 0.10-0.50mm »,</i>											
<i>Classic.</i>											
<i>« 13.40- 38.50 Broken zone. Near-surface breakage. FLT »« brco 30%»« flt bx 20%»« flt gg 10%»</i>											
<i>« 44.60- 62.60 Broken zone/minor fault FLT »« brco 20%»« flt bx 30%»</i>											
<i>« 71.80- 140.90 Flaggy mudstone with randomly oriented black stretches of bioturbated beds; Dark grey siliceous mudstone with bioturb is seen throughout the section. »</i>											
<i>« 76.20- 76.40 Qtz-calc supported breccia with flmd angular clasts 8-20 mm. »</i>											
<i>« 93.00- 99.50 qtz-calc veins are fully developed and cut through the black stretches of bioturb. »</i>											
<i>« @ 118.10 Bedding on the black stretches of bioturb S0 TCA 27° »</i>											
<i>« 119.60- 126.30 qtz-calc veining »</i>											

Selwyn Project Diamond Drill Log

Hole Number:
XYC-220

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
« 177.10- 130.20 Fault zone. FLT »« brco 40%»« flt bx 40%»« flt gg 5%»											
« 131.50- 134.50 Dark grey range »											
140.90	181.70	FLT	628501	179.20	180.70	1.50					
« Fault. Competent core is limestone and upper siliceous mudstone clasts. »« brco 30%»« flt bx 30%»« flt gg 10%»			628502	180.70	181.70	1.00					
181.70	252.40	ACTM	628503	181.70	182.20	0.50					
ACTM – Active Member			628504	182.20	183.70	1.50					
The ACTM consists of a repetitive, possibly rhythmic, sequence of intercalated carbonaceous mudstone, cherty mudstone, chert and limestone and locally contains economically significant Zn and Pb sulphides (see bold marked facies), mainly in its sections with well developed lamination. Because of its heterogeneity, the member is distinctive and easily identified. ===== The ACTM has 8 different facies: ===== - GREY CHERT FACIES: Consists of laminated medium light grey to medium dark grey chert. Mineralization: 95-99% quartz and up to 5% secondary calcite. - WHITISH GREY ZN-PB MUDSTONE FACIES: Is a laminated cherty rock containing up to 70% sulphides. Mineralization: quartz, sphalerite and galena are the major minerals with only minor amounts of pyrite and locally calcite. Sedimentary diagenetic structures are common and well displayed in the facies, such as: lamination, pseudo-beds, calcite nodules & limestone nodules and abundant water escape structures. Most obvious structure in facies is cross-cutting veins containing massive sphalerite and galena with minor pyrite. They range in width from 0.5 to 10mm. - THIN BEDDED CHERTY MUDSTONE FACIES: Consists of rhythmic intercalated laminae of chert, carbonaceous mudstone and minor micrite. This facies contains			628505	183.70	185.20	1.50					
			628506	185.20	186.70	1.50					
			628507	186.70	188.20	1.50					
			628508	188.20	188.90	0.70					
			628509	188.90	190.20	1.30					
			628510	190.20	191.50	1.30					
			628511	190.20	191.50	1.30					
			628512	191.50	192.60	1.10					
			628513	192.60	193.10	0.50					
			628514	193.10	194.20	1.10					
			628515	194.20	194.50	0.30					
			628516	194.50	195.00	0.50					
			628517	195.00	196.50	1.50					
			628518	196.50	198.00	1.50					
			628519	198.00	199.00	1.00					
			628520	199.00	199.00	0.00					
			628521	199.00	199.70	0.70					
			628522	199.70	201.20	1.50					
			628523	201.20	202.70	1.50					
			628524	202.70	204.20	1.50					
			628525	204.20	205.30	1.10					
			628526	205.30	205.70	0.40					
			628527	205.70	206.70	1.00					
			628528	206.70	207.70	1.00					
			628529	207.70	208.70	1.00					

Selwyn Project Diamond Drill Log

Hole Number:
XYC-220

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		significant amounts of Zn and Pb sulphides.	628530	208.70	208.70	0.00					
			628531	208.70	209.50	0.80					
		- <i>CHERTY MUDSTONE FACIES: Consists of a greyish black monotonous siliceous, carbonaceous mudstone. It is most typically found overlying the thin bedded calcareous mudstone facies.</i>	628532	209.50	210.80	1.30					
			628533	210.80	212.30	1.50					
			628534	212.30	213.80	1.50					
			628535	213.80	215.30	1.50					
		- <i>THIN BEDDED CALCAREOUS MUDSTONE FACIES: Consists of laminated carbonaceous mudstone containing 20-40% calcite, 40-55% quartz and 10-20% muscovite. Sulphides occur in laminae. In the XY area it is usually the lowest facies in the section to contain laminated sulphides.</i>	628536	215.30	216.50	1.20					
			628537	216.50	217.20	0.70					
			628538	217.20	218.70	1.50					
			628539	218.70	220.20	1.50					
			628540	220.20	221.70	1.50					
		- <i>CALCAREOUS MUDSTONE FACIES: Consists of grey to greyish black monotonous, calcareous siliceous carbonaceous mudstone. There are no feathery calcite beds or pyrite-calcite blebs in the facies, making it easily distinguishable from the CCMS.</i>	628541	220.20	221.70	1.50					
			628542	221.70	223.20	1.50					
			628543	223.20	224.50	1.30					
			628544	224.50	226.00	1.50					
			628545	226.00	227.50	1.50					
		- <i>GRADED LIMESTONE FACIES: Is a laminated argillaceous limestone with intercalated carbonaceous limestone laminae. The main rock type in the facies is laminated limestone with laminae up to 0.1-7mm thick.</i>	628546	227.50	229.00	1.50					
			628547	229.00	230.50	1.50					
			628548	230.50	232.00	1.50					
			628549	232.00	233.00	1.00					
		- <i>LIGHT GREY BASAL LIMESTONE FACIES - LGLS: Consists of laminated argillaceous limestone. In the Anniv area it marks the end of the ACTM. It's not always present in the stratigraphy.</i>	628550	233.00	233.00	0.00					
			628551	233.00	234.50	1.50					
			628552	234.50	235.60	1.10					
			628553	235.60	237.10	1.50					
		- <i>BASAL FACIES: This is a highly contorted and locally foliated carbonaceous mudstone. Unlike the other facies it is not repeated higher in the member. It appears locally to contain the slip zone of a major slump. The facies has only been observed in the YX area. It is 0.1-2m thick. The facies consists of massive carbonaceous siliceous mudstone with lenses and laminae of contorted, slightly carbonaceous chert.</i>	628554	237.10	238.60	1.50					
			628555	238.60	240.10	1.50					
			628556	240.10	241.60	1.50					
			628557	241.60	242.50	0.90					
			628558	242.50	243.50	1.00					
			628559	243.50	245.00	1.50					
			628560	245.00	245.00	0.00					
		All laminae are quite convoluted and mixed with limestone nodules.	628561	245.00	245.50	0.50					
			628562	245.50	247.00	1.50					

Selwyn Project Diamond Drill Log

Hole Number:
XYC-220

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
« 181.70- 182.20 »		Dark grey siliceous mudstone with bedding and laminae	628563	247.00	248.50	1.50					
			628564	248.50	250.00	1.50					
			628565	250.00	251.60	1.60					
			628566	251.60	252.40	0.80					
« 182.20- 188.20 Fault. Most clasts are broken limestone. FLT »« brco 50%»« flt bx 15%»« flt gg 5%»		« 188.20- 188.90 Medium grey siliceous mudstone with laminae but mineralization is less than 3% »									
« 188.90- 191.50 Light grey limestone with no dark strech but local qtz veining »		« 191.50- 192.60 Dark grey siliceous limestone with laminae. Estimated mineralization is less than 5%. »									
« 192.60- 193.10 Light grey limestone. »		« 193.10- 194.20 Medium grey siliceous limestone with laminae »									
« 193.10- 194.20 Medium grey siliceous limestone with laminae »		« 194.20- 194.50 Light grey limestone. »									
« 194.20- 194.50 Light grey limestone. »		« 194.50- 195.00 Dark grey siliceous mudstone with laminae »									
« 194.50- 195.00 Dark grey siliceous mudstone with laminae »		« 195.00- 199.00 Light grey limestone with local graded section »									
« 195.00- 199.00 Light grey limestone with local graded section »		« 199.00- 199.70 Dark grey calcareus mudstone with laminae. Mineralization <5% »									
« 199.00- 199.70 Dark grey calcareus mudstone with laminae. Mineralization <5% »		« 199.70- 205.30 Fault. Whole core remaining is limestone. FLT »« brco 40%»« flt bx 20%»« flt gg 5%»									
« 199.70- 205.30 Fault. Whole core remaining is limestone. FLT »« brco 40%»« flt bx 20%»« flt gg 5%»		« 205.30- 205.70 Light grey limestone with squiggly qtz-calc veins »									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-220

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
« 205.70- 209.50 Medium grey siliceous mudstone with laminae. Mineralization less than 5% »											
« 209.50- 210.80 Light grey coarser grained limestone »											
« 210.80- 217.20 Medium grey siliceous mudstone with laminae. Mineralization <1% »											
« 217.20- 224.50 Fault. Broken dark grey siliceous mudstone without laminae FLT »« brco 50%»« flt bx 10%»« flt gg 5%»											
« 224.50- 227.50 Light grey limestone »											
« 227.50- 233.00 Dark grey siliceous mudstone with no laminae; locally light grey liemstone nodules are seen; squiggly qtz-calc veins are present throughout the section »											
« 233.00- 235.60 Light grey limestone with dark stretch throughout section. qtz-calc veins are developed locally »											
« 235.60- 240.10 Fault in siliceous mudstone. Coarser grained, graded limestone with medium grey color appears in the bottom. FLT »« brco 50%»« flt bx 30%»« flt gg 5%»											
« 240.10- 242.50 Dark grey siliceous mudstone with no laminae »											
« 242.50- 243.50 Medium grey siliceous mudstone with laminae. Mineralization less than 10 % »											
« 243.50- 251.60 Light grey limestone »											
« 251.60- 252.40 Medium grey siliceous mudstone with laminae. Mineralization less than 5% »											
252.40	267.30	FLT	628567	252.40	253.00	0.60					

Selwyn Project Diamond Drill Log

Hole Number:
XYC-220

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		Fault. « Locally clast supported breccia are seen wit limestone clasts and dark grey siliceous mudstone clasts. Also, broken core of dark grey siliceous mudstone. »« brco 30%»« flt bx 40%»« flt gg 10%»	628568	253.00	254.50	1.50					
267.30	281.50	BSSM BSSM – Backside Siliceous Mudstone Devonian Siliceous Mudstone – Upper Chert Formation Greyish black laminated chert and siliceous mudstone. Randomly-oriented to bedding-parallel bioturbation is common in the bottom of the unit. « lm chrt 75.00-95.00% », « btrb 0.10-2.00cm », « 267.30- 275.60 Medium grey siliceous mudstone with occaisionally medium grey bioturbated sections. » « 275.60- 277.40 Fault in dark grey siliceous mudstone »« brco 60%»« flt bx 20%»« flt gg 5»									
281.50	281.50	EOH									

Diamond Drill Log

Comprehensive Report for Hole:

XYC-219

Hole No.: XYC-219	Depth: 354.20 m	Horizontal Length: 0.00 m	Project: 1710
Location Data:			
Property:	Selwyn Project	Claim Name:	X 2
Mining District:	Selwyn Basin	Grant Number:	Y 64527
Province/Territory:	Yukon		
UTM Co-Ordinates & Altitude of Drill Hole Collar:			
UTM Easting:	488218.00 m	True Azimuth:	0.0 °
UTM Northing:	6926810.00 m	Hole Angle:	-87.0 °
Elevation (m):	1574.00 m	NTS Name:	Placer Creek
		NTS Number:	105L06
Grid Co-Ordinates of Drill Hole Collar:			
Grid Easting (m):	0.00 m	Grid Name:	HP 06
Grid Northing (m):	0.00 m	Grid Type:	100m
Grid Azimuth:	60.0 °		
Dimond Drilling Contract:			
Drilled By:	NL-01	Date Drilling Start:	10/01/2010
		Date Finish:	10/10/2010
Diamond Drill Core:			
Logged By:	Graham Leroux	Date Logging Start:	10/12/2010
		Date Finish:	10/17/2010
Legend for Core Logging Codes: PAX			
Core Size:	NQ/NQ3	Cemented:	Yes
Casing Depth:	15.20 m	Casing Pulled:	Yes
Water Depth:	0.00 m	Overburden Depth:	15.20 m
Level:	Section:	Drift:	

Selwyn Project

Diamond Drill Log

Survey Data for Hole

XYC-219

Hole Comments:

Fri, Oct 01 --- XYC-209 got shut down yesterday late morning in CCMS. After pulling the rods, taking flexit tests and cementing from EOH to a depth of 520m, they moved the drill to target #34. Matt and Graham were there to line up the drill, but due to unexpected roadwork in order to get the drill to the setup and nightfall, it was not possible to finish the move yesterday evening.

Sat, Oct 02 --- Right now in BSSM at a total depth of 78m. About 15m of casing was put in.

Sun, Oct 03 --- Still in BSSM at a total depth of 111m. They drilled 33m in the past 24hrs.

Mon, Oct 04 --- Still in BSSM at a total depth of 177m. Bioturbations are present locally.

Tue, Oct 05 --- In FLMD at a depth of 213m

Wed, Oct 06 --- Still in FLMD at depth of 239m. Troubles at drill last night -- rubbers on the back-end could not go through landing rig, dropped core as a result.

Thu, Oct 07 --- Still in FLMD at depth of 261m.

Fri, Oct 08 --- Total depth of 304.8m in USMS

Sat, Oct 09 --- Total depth of 345m in CCMS. ACTM starts at 304.8m and ends at 329.2m in blocky ground, then CCMS to 345m.

Sun, Oct 10 --- At a total depth of 354m. Hole got shut down yesterday at 354m in CCMS. Nightshift, tested, pulled rods, cemented and got ready to move to set-up #14 today.

<i>Depth</i>	<i>Dip</i>	<i>Azimuth</i>
0.00	-87.0	0.0
50.00	-88.3	1.8
100.00	-89.6	216.5
150.00	-89.3	210.2
201.00	-87.5	206.5
250.00	-85.7	203.0
300.00	-85.4	203.2
350.00	-84.3	202.3

Selwyn Project Diamond Drill Log

Hole Number:
XYC-219

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
0.00	15.20	OVBR									
15.20	44.40	BSSM									
BSSM – Backside Siliceous Mudstone Devonian Siliceous Mudstone – Upper Chert Formation Greyish black laminated chert and siliceous mudstone. Randomly-oriented to bedding-parallel bioturbation is common in the bottom of the unit. « lm chrt 75.00-95.00% », « btrb 0.10-2.00cm », « 15.20- 28.40 Very blocky ground in graphitic, cherty laminated mudstone. Many minor areas of fault gouge. » « 28.40- 42.10 Dark grey laminated, siliceous and cherty laminae with minor wispy calcite conformable to S0. 2-7cm thick laminated sections of calcareous light grey laminae. Very minor pyrite, broken up along S0.» < @ 29.10 defined by calcic laminae S0, tca 60° > < @ 32.60 defined by laminae S0, tca 65° > < @ 35.60 defined by calcic lamiane S0, tca 65° > < @ 40.70 defined by wispy calcite S0, tca 65° > « 42.10- 44.40 Intercalated limestone and siliceous mudstone, with many fracture faces showing well developed pseudotachylite, Pyritic and cherty laminae in the mudstone. Mesothermal muddy veins cross-cutting through limestone. Some remineralized stylolites in mudstone.»											
44.40	260.40	FLMD									
FLMD – Flaggy Mudstone Formation											

Selwyn Project Diamond Drill Log

Hole Number:
XYC-219

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		Dark grey mudstone in the upper portions of the unit grading into light grey mudstone to siltstone. Contains abundant wispy bioturbation which ranges from randomly-oriented at the top of the unit to bedding-parallel throughout the majority of the unit. Darker upper section has a strong fetid odour along broken surfaces. « btrb 0.10-2.00cm », « cg xtl crns ca 1.00-5.00% 5.00-150.00cm », « crns py 1.00-5.00% 0.10-0.50mm », « 44.40- 46.60 Bioturbated light grey limestone and weakly laminated to massive muddy limestone, relatively coarse grained. No fetid odour on freshly broken surfaces. » « 46.60- 55.60 Weakly bioturbated medium grey mudstone, only weakly calcareous sections. Minor cherty laminae 2-4mm thick. Abundant pyrite nuodules mimic the trend of bioturbation and help to define S0. Many pyrite nodules are associated with calcite rims and range from 1-10mm in size. Discontinuous, squiggly, broken up pyrite (1-3mm thick). Recrystallized qt-cal veins up to 4-5cm thick. Minor pyrite laminae. » « @ 48.80 defined by laminae and pyrite nodules S0, tca 45° » « @ 48.90 defined by cherty laminae S0, tca 30° » « @ 50.80 defined by pyritic laminae S0. tca 15° » « @ 55.00 defined by bioturbations and pyritic nodules S0. tca 25° » « 55.60- 57.20 Muddy, bioturbated limestone with thick (1-20cm) recrystallized, coarse grained cal-qt veins. » « 57.20- 62.60 Medium grey weakly bioturbated mudstone with abundant chert nodules 1-4mm in lenth - and stretched out along S0. Numerous pyrite nodules as described with qt-cal rims. Two stages of calcic veining events. Early stage are thin (1-5mm) and broken up along S0, late stage are thicker (5-12mm) coarse-grained, with qt, and more nearly orthogonal to S0.»									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-219

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		< @ 59.30 defined by chert bioturbations S0, tca 25° > < @ 62.30 defined by laminae S0, tca 50° > « 62.60- 64.10 Muddy limestone, massive to weakly laminated. Entire interval is light to medium grey, with many sections that have lighter grey siliceous spots (2-6mm), could be graptolitic horizon? » « 64.10- 74.60 Medium to dark grey siliceous mudstone as described with pyritic nodules having qt rims with little or no calcite. Through this interval there are some laminae 2-12mm thick of massive pyrite that has been broken up by a later stage quartz veining event. This interval was broken out because it is far more blocky than other sections, with gouge developing on many fractures 1-3mm thick. » < @ 71.70 defined by pyritic/siliceous laminae S0, tca 50° > « 74.60- 84.00 medium to dark grey weakly bioturbated mudstone, chert and pyrite nodules as described. Pyritic zones are splotchy and appear bioturbated. » « 84.00- 85.70 FLT »« gg 10%»« bx 40%»« Brco 50%» « 85.70- 88.40 Coarse grained qt-cal intrusion, minor specs of incorporated country rock. » « 88.40- 93.40 Laminate, weakly bioturbated med-dk grey siliceous mudstone, some calcic and cherty bands, calcic ones are often associated with pyrite. Conchoidal fracture. » < @ 76.50 defined by bioturbation plane S0, tca 34° > < @ 91.70 defined by cherty laminae S0, tca 50° > « 93.40- 93.90 FLT »« gg 2%»« bx 50%»« Brco 48%»									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-219

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		« 93.90- 100.60 Dark grey laminated siliceous mudstone with discontinuous wispy calcite (feathery) laminae. Near base of interval calcareous content increases. Brown discontinuous laminae ~1-2mm thick are also a common feature of this interval. » « 100.60- 101.40 FLT »« gg 10%»« bx 30%»« Brco 60%» « 101.40- 102.50 Intercalated muddy laminated limestone with dark grey calcareous mudstone. Some qt-cal veins brecciate the country rock and incorporate it. » « 102.50- 102.90 FLT »« gg 50%»« bx 25%»« Brco 25%» < @ 95.00 defined by broken up brown laminae S0, tca 45° > « 102.90- 105.80 Competent interval of dk-grey mudstone as described » « 105.80- 106.90 FLT »« gg »« bx 50%»« Brco 50%» « 106.90- 116.90 Competent interval of dk-grey laminated mudstone, as previously described » < @ 107.80 defined by laminae S0, tca 42° > « 116.90- 117.30 FLT »« gg 50%»« Brco 50%» « 117.30- 128.10 Intercalated dk grey laminated mudstone with medium grey bioturbated mudstone and dark grey heterogeneous sections that look like USMS with squiggly chert and calcic laminae. Minor faulting throughout.» < @ 118.60 defined by laminae S0, tca 57° > < @ 124.00 defined by bioturbated laminae S0, tca 26° >									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-219

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		« 128.10- 138.40 Intercalated medium to light grey bioturbated typical of FLMD with medium grey laminated limestone. Abundant remineralized stylolites in the limestone, also some soft sediment deformation folding. Abundant calcite with quartz veining near the base of interval, first stage remineralizes stylolites, second stage infills fractures. » ◁ @ 130.40 defined by flaggy texture S0, tca 0% ▷ ◁ @ 135.30 defined by limestone laminae S0, tca 45° ▷ ◁ @ 138.10 defined by limestone laminae S0, tca 75° ▷ « 138.40- 157.8 dark grey siliceous, poorly laminated mudstone, intercalated with minor limestone. The mudstone has abundant wormy chert and calcic bands and soft sed deformation features. Calcite veining occurs in two stages. first stage typically 1-4mm thick remineralize stylolites and take on their shape. Late-stage infills fractures 0.2-4cm thick and have variable thickness throughout individual veins. Bunches of pyrite nodules cluster in a matrix of calcite and typically occur at major depositional boundaries 0.5-1.25m thick. Limestone concretions are commonly layered with limestone cores, a calcic halo then an outer pyritic layer. Cherty laminae can be broken up into discrete blobs that appear as nodules (typ 2-20mm). Some limestone concretions clearly deform the surrounding mudstone laminae. Minor faults throughout <10cm thick. » ◁ @ 144.90 defined by laminae S0, tca 32° ▷ « 157.80- 158.40 FLT »« gg 10%»« bx 40%»« Brco 50%» « 158.40- 160.70 Original description of this USMS-like unit applies here too » « 160.70- 171.5 Carbonaceous med-grey mudstone with abundant wormy limestone bands (3-8mm thick) contorted with S0. Intercalated with minor sections of FLMD (<20cm) and laminated limestone. Some of the limestone is									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-219

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		highly deformed and some is well laminated with wispy calcite conformable to S0 (about 50% of each limestone type). In lower part of this interval the FLMD component increases in abundance until at 171.5 there is a sharp depositional contact between the USMS- FLMD which may suggest this region of the hole is an overturned limb of a fold? Throughout the interval pyrite is the major sulphide mineral, occurring as speckelled laminae, clots disseminations and calcite brecciated concretions. » « 171.50- 260.40 Typical flaggy texture with weak to strong ichnofossil marks. Occassionaly the unit transitions between a dk-grey non-bioturbated sections of mudstone 5-60cm thick, then back into light grey bioturbated flaggy style mudstone. Angular to rounded calcic clasts (0.4-5cm) have dark grey mud-rich rims and disseminated pyrite throughout them. Also pyrite concretions with calcite rims. Disseminated pyrite throughout interval. Calcite veins have broken up massive pyrite in them. Systematic extensional type fractures occur discontinuously throughout. Some pyritic nodules have deformed S0 and suggest this unit is not actually overturned, but rather that there is just a sections of USMS within the flaggy unit. On many fracture surfaces there are disseminated blebs of pyrite and a fibrous bluish white mineral (anhydrite?). Framboidal pyrite concentrations. En-echelon tension gashes indicate a sinistral-sense of shear.» ◁ @ 184.20 defined by bioturbations S0 ×× Beta 213° ×× Alpha 18° ▷ ◁ @ 184.70 defined by bioturbations S0 ×× Beta 211° ×× Alpha 30° ▷ ◁ @ 188.50 defined by laminae S0 ×× Beta 228° ×× Alpha 30° ▷ ◁ @ 190.60 defined by bioturbations S0 ×× Beta 150° ×× Alpha 70° ▷ ◁ @ 197.90 defined by bioturbations S0 ×× Beta 182° ▷ ×× Alpha 58° ▷ ◁ @ 217.20 defined by laminae S0 ×× Beta 310° ×× Alpha 63° ▷ ◁ @ 220.40 defined by laminae S0 ×× Beta 345° ▷ ×× Alpha 44° ▷									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-219

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
260.40	304.50	USMS									
USMS – Upper Siliceous Mudstone			632451	301.80	302.70	0.90	0.02	0.01	1.00	5.00	4.00
Consists of interlaminated dark grey to black mudstone and light to medium grey chert. Regionally, a 1m thick graptolite zone occurs 15m below the top of the upper unit, this is usable as a horizon. The USMS is divided into 3 units. The Lower Unit contains abundant limestone concretions and Galena and sphalerite micro-concretions occur locally near the base of this unit. « gra , lm chrt -20.00% », « cg xtl sph crns ca 5.00-20.00cm », « bed chrt 10.00-15.00% », « 260.40- 304.50 Dark grey to blk carbonaceous mudstone, abundant wiggly calcic and cherty bands (3-10mm thick). Remineralized calcite stylolites. Interbedded with laminated and graded limestone (<10%). Patchy zones of brecciated pyrite, brecciated by quartz and calcite. Near the bottom of the interval there is an increase in limestone content coinciding with increases in mosaic-style thin (<2mm) calcite veinlets. S0 is variable, but most commonly is around 50 degrees.» « 300.90- 301.30 FLT »« gg 100%» « 302.70- 304.20 FLT »« gg 100%» < @ 267.90 S0 defined by graded limestone. S0 tca 50° > < @ 280.50 S0 defined by calcic and cherty laminae. S0 tca 50° > < @ 290.30 S0 defined by laminae S0 tca 50° >			632452	302.70	304.20	1.50	0.01	0.02	1.00	5.00	0.50
			632453	304.20	304.50	0.30	0.01	0.01	1.00	5.00	2.00
304.50	329.20	ACTM									
ACTM – Active Member			632454	304.50	306.40	1.90	0.08	0.33	1.00	10.00	0.24
The ACTM consists of a repetitive, possibly rhythmic, sequence of intercalated carbonaceous mudstone, cherty mudstone, chert and limestone and locally contains economically significant Zn and Pb sulphides (see bold marked facies),			632455	306.40	307.20	0.80	1.53	2.55	1.00	80.00	0.60
			632456	307.20	308.40	1.20	0.16	0.05	1.00	5.00	3.20
			632457	308.40	309.40	1.00	0.07	0.50	1.00	20.00	0.14
			632458	309.40	310.80	1.40	0.14	0.11	1.00	5.00	1.27
			632459	310.80	311.60	0.80	2.24	16.54	3.00	350.00	0.14

Selwyn Project

Diamond Drill Log

Hole Number:
XYC-219

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%	
mainly in its sections with well developed lamination. Because of its heterogeneity, the member is distinctive and easily identified. =====			632460	311.60	313.20	1.60	1.77	4.42	1.00	160.00	0.40	
			632461	311.60	313.20	1.60	2.43	4.81	1.00	160.00	0.51	
			632462	313.20	314.10	0.90	0.22	0.38	1.00	10.00	0.58	
			632463	314.10	314.90	0.80	4.40	5.36	3.00	190.00	0.82	
			632464	314.90	315.60	0.70	5.41	12.72	4.00	420.00	0.43	
			632465	315.60	318.10	2.50	2.74	5.70	1.00	160.00	0.48	
			632466	318.10	318.80	0.70	2.38	12.30	3.00	310.00	0.19	
			632467	318.80	319.20	0.40	6.63	14.34	3.00	540.00	0.46	
			632468	319.20	320.30	1.10	0.36	3.09	1.00	90.00	0.12	
			632469	320.30	321.50	1.20	0.73	2.51	1.00	80.00	0.29	
			632470	321.50	321.50	0.00	0.01	0.01	1.00	5.00	2.00	
				632471	321.50	322.80	1.30	0.76	2.23	1.00	90.00	0.34
				632472	322.80	323.60	0.80	0.42	1.32	1.00	60.00	0.32
				632473	323.60	324.30	0.70	6.39	13.53	3.00	560.00	0.47
				632474	324.30	325.70	1.40	13.36	28.03	5.00	1270.00	0.48
				632475	325.70	326.50	0.80	13.18	20.59	5.00	1040.00	0.64
				632476	326.50	327.20	0.70	12.79	19.20	8.00	890.00	0.67
				632477	327.20	328.10	0.90	2.89	3.15	3.00	150.00	0.92
				632478	328.10	329.20	1.10	0.33	0.36	1.00	20.00	0.92

Selwyn Project Diamond Drill Log

Hole Number:
XYC-219

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		calcareous siliceous carbonaceous mudstone. There are no feathery calcite beds or pyrite-calcite blebs in the facies, making it easily distinguishable from the CCMS. - GRADED LIMESTONE FACIES: Is a laminated argillaceous limestone with intercalated carbonaceous limestone laminae. The main rock type in the facies is laminated limestone with laminae up to 0.1-7mm thick. - LIGHT GREY BASAL LIMESTONE FACIES - LGLS: Consists of laminated argillaceous limestone. In the Anniv area it marks the end of the ACTM. It's not always present in the stratigraphy. - BASAL FACIES: This is a highly contorted and locally foliated carbonaceous mudstone. Unlike the other facies it is not repeated higher in the member. It appears locally to contain the slip zone of a major slump. The facies has only been observed in the YX area. It is 0.1-2m thick. The facies consists of massive carbonaceous siliceous mudstone with lenses and laminae of contorted, slightly carbonaceous chert. « 304.50- 306.40 Very carbonaceous fault gouge and breccia pieces. Slick-n-lines are well developed on brecciated pieces. XRF: Pb 0.210% Zn:0.535 sweeping avg. Flt »« Flt gg 90%»« Flt bx 10%» « 306.40- 314.90 Highly faulted region. Increases in calcareous component tends to resist turning into gouge. All gouge is carbonaceous and has well developed pseudotachylite. The interval consists of heavily calcite-veined bluish-grey limestone and carbonaceous fault gouge and breccia. Some gouge zones have been partially recemented by calcite. The limestone is massive to laminated. One section at ~308.0m has ~10cm thick bed of massive pyrite. Flt »« Flt gg 30%»« Flt bx 30%»« Brco 30%» « 306.40- 307.20 Pb: 1.38%; Zn: 2.26% » « 307.20- 308.40 Pb: 0.318%; Zn: 0.104% » « 308.40- 309.40 Pb: 0.267%; Zn: 0.314% »									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-219

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		« 309.40- 310.80 Pb: 0.267%; Zn: 0.211% » « 310.80- 311.60 Pb: 1.06%; Zn: 4.56% » « 311.60- 313.20 Pb: 7.43%; Zn: 4.71% » « 313.20- 314.10 Pb: 1.28%; Zn: 1.38% » « 314.10- 314.90 Pb: 5.10%; Zn: 5.89% » « 314.90- 315.60 Pb: 15.55%; Zn: 10.13% Light to medium-grey, heavily fractured laminated and graded limestone. Coarse quartz and calcite infill fractures, and coarse yellowish sphalerite also occurs as blebs in some fractures. For the most part base metals enrich laminae and some fractures. » « 315.60- 318.10 Pb: 15.55%; Zn: 10.13% Very blocky ground of carbonaceous mudstone. Abundant calcite infilled fractures. Pyritic calcareous mudstone clasts 3-8cm diameter with sub-rounded boundaries. FLT»« Flt gg 15%»« Flt bx 50%»« Brco 35%» « 318.10- 318.80 Pb: 5.19%; Zn: 12.47% Laminated light-grey limestone with a high mud component. Recrystallized calcite-qt veins. Sphalerite laminae and barren laminae are interbedded ~ <1-3mm thick laminae. » « 318.80- 319.20 Pb: 37.10%; Zn: 21.56% Interlaminated limestone, sphalerite and galena ore with micritic layers. Coarse galena and sphalerite blebs are remobilized with calcite and quartz randomly oriented veins. » « 319.20- 320.30 Pb: 0.527%; Zn: 1.41% Laminated muddy limestone. S0 approaches 0 degrees. Calcite remineralized stylolites, also randomly oriented veins. » « 320.30- 321.50 Pb: 0.506%; Zn: 0.919% Heavily fractured and calcite veined coarse-fine grained limestone. Clastic appearance in lower part of interval. Some calcite veins mobilize blebs of sphalerite in trace amounts. » « 321.50- 322.80 Pb: 1.21%; Zn: 1.75% Carbonaceous and calcareous dark-grey to black mudstone, blocky ground with some reconstituted breccia cemented together by calcite and quartz. »									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-219

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
« 322.80- 323.60 Pb: 0.895%; Zn: 1.26% Laminated limestone, many more sphalerite-rich laminae (1-2%). Weakly graded laminae. Coarse-grained calcite-quartz veins cross-cut laminae. » « 323.60- 327.20 Light grey clastic laminated limestone. Interlaminated galena-rich and sphalerite laminae. Upper part of interval is highly fractured with abundant calcite blebs and limestone clasts, which gradually change into regularly laminated ore rock near bottom of interval. Laminae can be slightly wavy and attitude is highly variable. » « 323.60- 324.30 Pb: 9.33%; Zn: 8.86% » « 324.30- 325.70 Pb: 62.40%; Zn:36.22% Inflated » « 325.70- 326.50 Pb: 68.02%; Zn: 29.32% Inflated » « 326.50- 327.20 Pb: 69.35%; Zn: 27.99% Inflated » « 327.20- 328.10 Pb: 2.30%; Zn: 1.43% Transitional zone between high-grade ore zone in low-grade calcareous mudstone. Interlaminated limestone, carbonaceous mudstone, pyritic laminae, calcic laminae.» « 328.10- 329.20 Pb: 0.158%; Zn: 0.077% Weakly calcareous, carbonaceous massive mudstone. Dark-grey to black pyritic fragments are randomly oriented. Abundant pseudotachylite and quartz-calcite veining. »											
329.20	354.20	CCMS	632479	329.20	330.00	0.80	0.03	0.17	1.00	10.00	0.18
CCMS – Calcareous Mudstone			632480	330.00	330.00	0.00	5.92	6.97	70.00	180.00	0.85
			632481	330.00	331.10	1.10	0.01	0.10	1.00	5.00	0.10
Massive, calcareous, carbonaceous, dark grey mudstone. Most of the member is massive, but rare poorly defined bedding and pyrite-calcite micro-concretions are present. Most diagnostic structures are feathery calcite beds (=thin calcite-cemented concretions, many of them contain pyrite cores) and calcite pseudo-beds (= fibrous calcite vein parallel to bedding).											

Selwyn Project Diamond Drill Log

Hole Number:
XYC-219

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		« lm ca 5.00-10.00mm », « nodules py -3.00% 2.00-20.00mm »									
		« 329.20- 330.00 Carbonaceous mudstone. Shoulder sample. Zn: 0.155% Flt » « Flt gg 50%»« Flt bx 50%»									
		« 330.00- 331.10 Carbonaceous mudstone, shoulder sample. Flt »« Flt gg 45%»« Flt bx 45%»« Brco 10%»									
		« 331.10- 333.90 Flt »« Flt gg 15%»« Flt bx 65%»« Brco 20%»									
		« 333.90- 346.90 Dark grey monotonous weakly laminated mudstone, wispy discontinuous calcite veinlets. Pyritic and calcite blow-outs up to 7cm, rare though. Abundant minor faults with slick-n-lines on pseudotachylite, slippage is plane-parallel. »									
		« 346.90- 354.20 Flt »« Flt gg 50%»« Flt bx 30%»« Brco 20%»									
		« @ 339.00 S0 defined by laminae S0 tca 50° »									
354.20	354.20	EOH									

Selwyn Project

Diamond Drill Log

Comprehensive Report for Hole:

XYC-218

Hole No.: XYC-218	Depth: 195.30 m	Horizontal Length: 0.00 m	Project: 1710
Location Data:			
Property:	Selwyn Project	Claim Name:	X 2
Mining District:	Selwyn Basin	Grant Number:	Y 64527
Province/Territory:	Yukon		
UTM Co-Ordinates & Altitude of Drill Hole Collar:			
UTM Easting:	488214.00 m	True Azimuth:	210.0 °
UTM Northing:	6926731.00 m	Hole Angle:	-65.0 °
Elevation (m):	1535.00 m	NTS Name:	Placer Creek
		NTS Number:	105L06
Grid Co-Ordinates of Drill Hole Collar:			
Grid Easting (m):	0.00 m	Grid Name:	HP 06
Grid Northing (m):	0.00 m	Grid Type:	100m
Grid Azimuth:	270.0 °		
Dimond Drilling Contract:			
Drilled By:	NL-02	Date Drilling Start:	09/29/2010
		Date Finish:	10/01/2010
Diamond Drill Core:			
Logged By:	Graham Leroux	Date Logging Start:	10/03/2010
		Date Finish:	10/05/2010
Legend for Core Logging Codes: PAX			
Core Size:	NQ/NQ3	Cemented:	Yes
Casing Depth:	18.20 m	Casing Pulled:	Yes
Water Depth:	0.00 m	Overburden Depth:	18.20 m
Level:	Section:	Drift:	

Selwyn Project

Diamond Drill Log

Survey Data for Hole

XYC-218

Hole Comments:

Wed, Sep 29 --- XYC-217 got shut down yesterday afternoon at a total depth of 135.5m. CLST was encountered at a depth of 103m. A fault was observed a few meters just before that. After the rods got pulled and the hole cemented, the drill got moved to target 33. As of this morning, 60' (18.3) of casing was put down.

=====

Thu, Sep 30 --- The hole is in USMS at a total depth of 80.1m. The core is fairly broken up.

=====

Fri, Oct 01 --- The hole is at a total depth of 127.1m and in ACTM. The ACTM was encountered at an approximate depth of 119m.

=====

Sat, Oct 02 --- The drill got shut down yesterday evening, the hole got cemented and they are ready to move as of this morning shift change. ACTM was intersected from 119m to 126m; ACTM interval was nothing noteworthy. Then a fault was intersected from 126m to 128.7m. After that all CLST until EOH. This drill will move onto target #45.

<i>Depth</i>	<i>Dip</i>	<i>Azimuth</i>
0.00	-65.0	210.0
50.00	-64.1	209.2
100.00	-63.6	211.3
150.00	-61.1	207.7
195.80	-59.5	207.3

Selwyn Project Diamond Drill Log

Hole Number:
XYC-218

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
0.00	18.20	OVBR									
18.20	119.00	USMS	632401	117.50	118.60	1.10	0.04	0.15	1.00	10.00	0.27
USMS – Upper Siliceous Mudstone			632402	118.60	119.00	0.40	0.77	1.87	1.00	60.00	0.41
Consists of interlaminated dark grey to black mudstone and light to medium grey chert. Regionally, a 1m thick graptolite zone occurs 15m below the top of the upper unit, this is usable as a horizon. The USMS is divided into 3 units. The Lower Unit contains abundant limestone concretions and Galena and sphalerite micro-concretions occur locally near the base of this unit. « gra , lm chrt -20.00% », « cg xtl sph crns ca 5.00-20.00cm », « bed chrt 10.00-15.00% », « 18.20- 20.60 Carbonaceous and slightly calcareous mudstone, highly fractured and many thin zones of fault gouge. Recrystallized quartz and calcite in veins. Lots of pseudotachylite among the many broken surfaces. Numerous wormy calcite veins and calcareous patches. » « 20.60- 29.30 More cohesive, carbonaceous and slightly calcareous mudstone. Some areas show a lamination defined by wispy calcite and/or pyrite. Many fracture surfaces have pseudotachylite and slick-n-lines on them. Pressure dissolution seams are pitted. There are at least two stages of calcite-quartz veining. Extensional-type appear to be the later stage. Micro-pyrite blebs are minor in amount, but pervasive. » « @ 24.70 defined by calcareous laminae S0 42° tca » « 29.30- 32.90 fault »« gg 2%»« bx 75%»« Brco 23%»« despite there being significant amounts of broken core, this whole range is highly veined and mostly fault breccia » « 32.90- 35.40 Cohesive core, typical carbonaceous USMS with extensional veining and broken up wormy calcareous bands that can be associated with pyrite blebs. »											

Selwyn Project Diamond Drill Log

Hole Number:
XYC-218

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		«35.40- 36.20 fault »« gg 25%»« bx 60%»« Brco 15%»									
		« 36.20- 43.60 Range of increased calcite veining and related rock fracturing. Patchy , discontinuous zones grade up to 0.1% combined Pb/Zn. Bedding is defined by convoluted laminae, not worth measuring. Abundant infilled stylolites and blocky fractured calcite+/- quartz veins. Calcareous component increases in lower half of interval. Many specular blebs of pyrite with rims of calcite-quartz. Lots of extensional fracture veins and recrystallized quartz.»									
		« 43.60- 43.80 fault »« gg 95%»« bx 5%»« Brco »									
		« 43.80- 53.40 Carbonaceous and slightly clacareous mudstone, pervasive specular pyrite and blebby pyrite associated with recrystallized calcite-quartz. Remineralized irregular stylolites. Broken up calcareous laminae? or thin concretions? Limestone concretions on cm-scale are graded and fine to medium grained. Some patches are highly calcareous. Laminations are highly irregular, but in some areas there appears to be some consistency.»									
		« @ 50.90 S0 defined by graded calcareous mudstone S0 tca 47° »									
		« 53.40- 119.00 fault -- very large fault range. There is so much faulting here that it does not seem right to break out core pieces as intervals. The largest core pieces are <50cm. There is up to 60% calcite alteration that is associated with minor quartz. There is an abundance of cm-scale limestone concretions throughout the range. fault »« gg 25%»« bx 50%»« Brco 25%»									
		« 117.50- 118.30 Outer shoulder sample, approx. 100% fault gouge (part of large fault interval) There is abundant calcite infill in the upper part of the interval. The gouge is soft and crumbly, very carbonaceous and calcareous. Pyrite bands are 0.9- 1.2cm thick and evident in a few locations. Where pyrite concentrates there is an increase in base metal mineralization. [Pb: 0.139%, Zn: 0.268%] »									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-218

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
« 118.60- 119.00 Inner shoulder sample. Again this sample is all carbonaceous and calcareous fault gouge. Minor bluish alteration mineral present (anhydrite?). [Pb: 0.454%, Zn: 0.749%]»											
119.00	125.50	ACTM	632403	119.00	120.20	1.20	4.03	16.36	1.00	450.00	0.25
ACTM – Active Member			632404	120.20	121.50	1.30	1.17	6.34	1.00	160.00	0.18
The ACTM consists of a repetitive, possibly rhythmic, sequence of intercalated carbonaceous mudstone, cherty mudstone, chert and limestone and locally contains economically significant Zn and Pb sulphides (see bold marked facies), mainly in its sections with well developed lamination. Because of its heterogeneity, the member is distinctive and easily identified. ===== The ACTM has 8 different facies: ===== - GREY CHERT FACIES: Consists of laminated medium light grey to medium dark grey chert. Mineralization: 95-99% quartz and up to 5% secondary calcite. - WHITISH GREY ZN-PB MUDSTONE FACIES: Is a laminated cherty rock containing up to 70% sulphides. Mineralization: quartz, sphalerite and galena are the major minerals with only minor amounts of pyrite and locally calcite. Sedimentary diagenetic structures are common and well displayed in the facies, such as: lamination, pseudo-beds, calcite nodules & limestone nodules and abundant water escape structures. Most obvious structure in facies is cross-cutting veins containing massive sphalerite and galena with minor pyrite. They range in width from 0.5 to 10mm. - THIN BEDDED CHERTY MUDSTONE FACIES: Consists of rhythmic intercalated laminae of chert, carbonaceous mudstone and minor micrite. This facies contains significant amounts of Zn and Pb sulphides. - CHERTY MUDSTONE FACIES: Consists of a greyish black monotonous siliceous, carbonaceous mudstone. It is most typically found overlying the thin bedded			632405	121.50	122.20	0.70	1.84	7.15	1.00	150.00	0.26
			632406	122.20	123.10	0.90	1.42	8.87	1.00	210.00	0.16
			632407	123.10	123.50	0.40	2.89	8.92	1.00	270.00	0.32
			632408	123.50	124.30	0.80	2.93	17.73	1.00	430.00	0.17
			632409	124.30	125.50	1.20	5.35	7.61	2.00	340.00	0.70

Selwyn Project Diamond Drill Log

Hole Number:
XYC-218

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		calcareous mudstone facies. - <i>THIN BEDDED CALCAREOUS MUDSTONE FACIES: Consists of laminated carbonaceous mudstone containing 20-40% calcite, 40-55% quartz and 10-20% muscovite. Sulphides occur in laminae. In the XY area it is usually the lowest facies in the section to contain laminated sulphides.</i> - <i>CALCAREOUS MUDSTONE FACIES: Consists of grey to greyish black monotonous, calcareous siliceous carbonaceous mudstone. There are no feathery calcite beds or pyrite-calcite blebs in the facies, making it easily distinguishable from the CCMS.</i> - <i>GRADED LIMESTONE FACIES: Is a laminated argillaceous limestone with intercalated carbonaceous limestone laminae. The main rock type in the facies is laminated limestone with laminae up to 0.1-7mm thick.</i> - <i>LIGHT GREY BASAL LIMESTONE FACIES - LGLS: Consists of laminated argillaceous limestone. In the Anniv area it marks the end of the ACTM. It's not always present in the stratigraphy.</i> - <i>BASAL FACIES: This is a highly contorted and locally foliated carbonaceous mudstone. Unlike the other facies it is not repeated higher in the member. It appears locally to contain the slip zone of a major slump. The facies has only been observed in the YX area. It is 0.1-2m thick. The facies consists of massive carbonaceous siliceous mudstone with lenses and laminae of contorted, slightly carbonaceous chert.</i> « This whole interval is mylonitic, full of fault breccia and fault gouge. Only a few pieces of core are preserved, they are typically <30cm long . This ACTM interval was most likely brought into place by faulting. The broken core is very heavily mylonitized and close to being gouge. Split tubes have done an excellent job bringing this section out of the hole at all»« fault »« gg 25%»« bx 25%»« Brco 50%»									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-218

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		« 119.00- 120.20 Finely laminated carbonaceous and calcareous, mylonitic mudstone with patches of gouge that have fragmental mudstone in them. Light yellowish grey bands are wrich in sphalerite. Galena mineralization is conformable with laminae and shear-sense. Late-stage recrystallized calcite infills interstitially to some gouge zones. Mudstone fragments in gouge zone have two early calcifying events. Earliest stage occurs as micro wispy conformable laminae, later-stage calcite infills tension fractures. [Pb: 6.70%, Zn: 12.38%]» « 119.00- 121.50 Upper 8cm is black fault gouge, the remainder of the interval is medium greyish to black and heavily mylonitized. High grade laminae are discontinuous and no greater than 10cm long. Recrystallized quartz-calcite veins are pervasive. Of the observable sections of actual rock - dark carbonaceous mudstone is intercalated with med-grey calcareous mudstone. [Pb: 1.31%, Zn: 3.90%]» « 121.50- 122.20 Upper 6cm has combined XRF grade of >40%, with high Pb values in excess of 30% giving inflated readings. This high grade section is too small to sample on its own, it is carbonaceous and slightly calcareous with wavy irregular laminae. The remainder of the interval has similar geometry, is more heavily affected by faulting as gouge component increases along with carbon content. There are only minor sections where veining style is preserved, and it is the same as previously described, most veining however is all broken up in the faulting. [Pb: 1.86%, Zn: 3.83%] . » « 122.20- 123.10 Lower part of the interval has ~6cm of high grade zinc (Zn > 12%), the rest has patchy high grade zones of < 1-2cm that are fractured and displaced within a mostly barren carbonaceous fault gouge. Medium grey calcareous laminae are sometimes preserved within the gouge. At the lower part of the interval, increases of calcite content is associated with increases in yellowish sphalerite mineralization. [Pb: 1.97%, Zn: 5.33%]. » « 123.10- 123.50 This interval represents the rock most unaffected by faulting, still however it is sheared and fractured. The upper part of the									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-218

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		interval hosts an approx 10cm thick calcite +/- quartz vein that has incorporated fragments of the country rock. The vein itself is not uniform in composition - it has carbonaceous mudstone irregular veinlets running through it. The host/country rock here is dirty limestone, moderately laminated, with broken up calcite veins and laminae. One could say there is a flaggy mudstone appearance to the lower part of the interval. Galena is mostly very fine grained and remobilized in discordant veins/fractures. [Pb: 2.92%, Zn: 4.12%]»									
		« 123.50- 124.30 Only 50% core recovery over this run. Upper part of interval is finely laminated yellowish to med-grey calcareous mudstone with vfg sphalerite and interstitial galena. Minor calcite laminae and broken up calcite +/- quartz fragments. The whole interval is mylonitic, as this is still part of the major fault region. Lower part of interval has abundant gouge development and is highly carbonaceous, moderately calcareous. [Pb: 2.81%, Zn: 8.56%]. »									
		« 124.30- 125.50 Muddy laminated limestone. Upper part of interval gouge-rich and mylonitic, lower part has laminae and sphalerite bands preserved. Right at the bottom of interval, faulting has resulted in limestone mosaic-style fragments in a mud/gouge matrix. Broken up and boudinaged calcite+quartz is common. [Pb: 5.69%, Zn: 4.25%]»									
125.50	128.70	FLT	632410	125.50	126.90	1.40	0.04	0.07	1.00	5.00	0.57
			632411	125.50	126.90	1.40	0.02	0.08	1.00	5.00	0.25
		« 125.50- 128.70 fault »« gg 100%»	632412	126.90	128.00	1.10	0.01	0.04	1.00	5.00	0.25
			632413	128.00	128.00	0.00	0.01	0.01	1.00	5.00	2.00
		« 125.50- 126.90 Greyish black to black fault gouge, broken up calcite veins and blow-outs. Very carbonaceous. No primary features remain. [Pb: 0.102%, Zn: 0.146%]»	632414	128.00	128.70	0.70	0.01	0.01	1.00	5.00	1.00
		« 126.9- 128.0 Outer shoulder sample, still all black, soft, carbonaceous fault gouge. [Zn: 0.083%].»									
		« 128.00- 128.70 Barren carbonaceous fault gouge. Interval end is marked by a sharp unconformity contact with TRAN. Units not intersected in the									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-218

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
footwall: LCMS, CCMS, PSMS.»											
128.70	155.20	TRAN	632415	128.70	128.70	0.00	1.40	2.89	20.00	180.00	0.48
TRAN – Transition Formation											
Consists of laminated tan mudstone and minor intercalated light grey limestone. « lm mdst 1.00-10.00mm », « 128.70- 155.20 Intercalated calcareous light grey mudstone with abundant oblong and irregular fine grained massive limestone concretions. Laminae are cross-bedded and occassionally are wavy in a similar style as CLST; however, with significantly less calcareous component. Entire interval is heavily veined with fine irregular calcite veinlets. The majority of tension gashes are offset in a dextral-sense and infilled with calcite +/- minor quartz. Lower contact with CLST is well defined by a change into more regular wavy, cross-bedded laminae that are significantly more calcareous. Laminae are highly contorted, which makes taking S0 measurements variable; however, I have tried to take S0 measurements systematically to see if there is any consistency within the oriented core. » < @ 136.10 wavy contorted laminae S0 > < Beta 360° > < Alpha, 27° tca > < @ 139.90 wavy contorted laminae S0 > < Beta 344° > < Alpha, 45° tca > < @ 142.60 conformable limestone band S0 > < Beta 358° > < Alpha, 35° tca > < @ 149.80 wavy contorted laminae S0 > < Beta 360° > < Alpha, 54 tca > « These four measurements are the best representation of the rock geometry in the footwall to the active member; however convoluted and cross-bedded, intercalated and truncated depositional layers are -- there appears to be some consistency to the geometry. All shear zones must start and end - the major shearing intersected in this hole starts significantly altering the rock around 50m depth in the USMS unit. The end zone of strain features occurs around the contact between TRAN-CLST at											

Selwyn Project Diamond Drill Log

Hole Number:
XYC-218

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		~150m depth. The majority of kinematic indicators suggest a dextral-sense shearing with subordinate, antithetic faulting occurring in a sinistral-sense. The implication being that the faulting that 'brought in' the ACTM to an uncomformable position with TRAN occurred in a dextral fashion (from left to right). The most common structural feature that outlines this movement are semi-brittle dextral shears that form sets of en-echelon calcite +/- quartz tension gashes. » « Please refer to paper log for sketch and rough outline of a possible strain ellipsoid. »									
155.20	195.30	CLST CLST – Cambrian Limestone Consists of 2 units. The first unit, Wavy Banded Limestone Formation, is divided into two informal members, based on the amount of argillaceous material in some beds. Both members display well-banded limestone. The upper member consists of intercalated light grey siliceous micrite and grey to tan laminated calcareous mudstone beds, displaying a chain-link structure. It appears wavy because of variable bedding thickness. Bedding is in general thinner than the bedding in the lower member, with micrite beds ranging from 1 to 5 cm thick, and showing rapid lateral variation. The lower member consists of intercalated microspar and micrite, and shows even bedding. The second unit, Massive Limestone Formation, consists of massive grey, micritic siliceous limestone. « lt gra , lm microspar 5.00-40.00cm », « lm micrite 1.00-5.00cm », « gra to lt bro , calcareous mdst 5.00-30.00mm », « 155.20- 195.30 Classic style of the upper member to the wavy banded limestone formation. There are weak representations of ductile and brittle shearing, the rock is still all in tact and competent. Some recrystallized blow-outs of calcite interrupt the 'chain-link' style and occur with minor quartz. Most cal-qt veins are orthogonal to S0 and are impressively systematic with attitude, on average they are 1cm thick. Rare occurrence of pyrite nodules, no bigger than 2mm in di. The general description of this unit does									

Selwyn Project

Diamond Drill Log

Hole Number:
XYC-218

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
also apply to this interval. »											
< @ 155.30 defined by wavy laminae S0 > < Beta 166° > < Alpha, 44° tca>											
< @ 157.90 defined by wavy laminae S0 > < Beta 215° > < Alpha, 46° tca>											
< @ 159.40 defined by wavy laminae S0 > < Beta 175° > < Alpha, 45° tca>											
< @ 171.90 defined by wavy laminae S0 > < Beta 203° > < Alpha, 31° tca>											
< @ 174.70 defined by wavy laminae S0 > < Beta 203° > < Alpha, 33° tca>											
< @ 180.90 defined by wavy laminae S0, tca 35° >											
< @ 183.90 defined by wavy laminae S0, tca 35° >											
< @ 186.40 defined by wavy laminae S0, tca 38° >											
< @ 191.40 defined by wavy laminae S0, tca 34° >											
< @ 195.20 defined by wavy laminae S0 35° >											
195.30	195.30	EOH									

Selwyn Project

Diamond Drill Log

Comprehensive Report for Hole:

XYC-217

Hole No.: XYC-217	Depth: 135.50 m	Horizontal Length: 0.00 m	Project: 1710
Location Data:			
Property:	Selwyn Project	Claim Name:	X 2
Mining District:	Selwyn Basin	Grant Number:	Y 64527
Province/Territory:	Yukon		
UTM Co-Ordinates & Altitude of Drill Hole Collar:			
UTM Easting:	488237.00 m	True Azimuth:	203.0 °
UTM Northing:	6926658.00 m	Hole Angle:	-70.0 °
Elevation (m):	1522.00 m	NTS Name:	Placer Creek
		NTS Number:	105L06
Grid Co-Ordinates of Drill Hole Collar:			
Grid Easting (m):	0.00 m	Grid Name:	HP 06
Grid Northing (m):	0.00 m	Grid Type:	100m
Grid Azimuth:	263.0 °		
Dimond Drilling Contract:			
Drilled By:	NL-02	Date Drilling Start:	10/26/2010
		Date Finish:	10/28/2010
Diamond Drill Core:			
Logged By:	Matt Jodrey	Date Logging Start:	Date Finish:
Legend for Core Logging Codes: PAX			
Core Size:	NQ	Cemented:	Yes
Casing Depth:	14.00 m	Casing Pulled:	Yes
Water Depth:	0.00 m	Overburden Depth:	14.00 m
Level:	Section:	Drift:	

Selwyn Project

Diamond Drill Log

Survey Data for Hole

XYC-217

Hole Comments:

Mon, Sep 27 --- XYC-213 got shut down yesterday morning. The drill move to target #30 started late in the afternoon, after the CY-01 drill move was finished. Drilling commenced around early evening. 50' of casing was put in. The hole is at 33m and is very probably in USMS. Core is badly broken up.

=====

Tue, Sep 28 --- At a total depth of 99.5m. Yesterday they hit ACTM at 43.3m. This morning it seems we're (almost)? out of the ACTM, as a piece in the last box ran 0.7%Zn. This could be either barren ACTM or footwall rocks, as I have seen these low Zn grades in CCMS before.

=====

Wed, Sep 29 --- XYC-217 got shut down yesterday afternoon at a total depth of m. After the rods got pulled and the hole cemented, the drill got moved to target 33.

<i>Depth</i>	<i>Dip</i>	<i>Azimuth</i>
0.00	-70.0	203.0
50.00	-68.7	203.7
99.00	-67.8	205.4

Selwyn Project Diamond Drill Log

Hole Number:
XYC-217

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
0.00	14.00	OVBR									
14.00	63.90	FLT	633601	43.30	44.40	1.10	0.51	3.77	2.00	140.00	0.14
« 14.00- 63.90 Major carbonaceous fault zone with abundant fault breccia and fault gouge. Competent fragments from various units are visible within the fault zone, suggesting significant re-working of material and displacement. Flt »« Flt gg 20%»« Flt bx 50%» « 14.00- 17.70 Fault material derived from FLMD. » « 17.70- 38.30 Fault material derived from BSMS » « 38.30- 40.50 Fault material derived from FLMD. » « 43.30- 44.40 Fault material from ACTM. Sampling interval started here. Competent segments consist of finely laminated calcareous mudstone with disseminated mineralization, mixed with LMST. Moderate to strong mineralization (5-12% combined throughout range). Brecciated, deformed structure. Broken up. » « 44.40- 63.90 Primarily fault gouge and breccia. Poor core recovery over 54.5-63.9m. Fault material appears to be derived from BSMS. »			633602	44.40	44.80	0.40	0.20	0.19	1.00	10.00	1.05
			633603	44.80	46.10	1.30	0.06	0.80	1.00	40.00	0.08
			633604	46.10	47.30	1.20	0.01	0.02	1.00	5.00	0.50
			633605	47.30	50.30	3.00	0.01	0.06	3.00	5.00	0.17
			633606	50.30	51.50	1.20	0.11	0.01	1.00	5.00	22.00
			633607	51.50	53.00	1.50	0.03	0.01	2.00	5.00	3.00
			633608	53.00	54.20	1.20	0.01	0.01	1.00	5.00	2.00
			633609	54.20	63.90	9.70	0.02	0.13	1.00	10.00	0.15
63.90	77.90	ACTM	633610	63.90	64.90	1.00	2.59	12.08	3.00	520.00	0.21
ACTM – Active Member The ACTM consists of a repetitive, possibly rhythmic, sequence of intercalated carbonaceous mudstone, cherty mudstone, chert and limestone and locally contains economically significant Zn and Pb sulphides (see bold marked facies), mainly in its sections with well developed lamination. Because of its heterogeneity, the member is distinctive and easily identified. ===== The ACTM has 8 different facies: =====			633611	63.90	64.90	1.00	2.20	12.38	5.00	560.00	0.18
			633612	64.90	65.90	1.00	3.03	7.62	6.00	310.00	0.40
			633613	65.90	66.40	0.50	4.35	11.97	5.00	560.00	0.36
			633614	66.40	67.80	1.40	4.01	8.30	4.00	320.00	0.48
			633615	67.80	69.10	1.30	0.24	0.49	1.00	20.00	0.49
			633616	69.10	72.40	3.30	5.80	4.65	2.00	120.00	1.25
			633617	72.40	76.00	3.60	0.94	2.85	1.00	90.00	0.33
			633618	76.00	76.40	0.40	0.01	0.01	1.00	5.00	2.00
			633619	76.40	77.00	0.60	0.01	0.01	1.00	5.00	2.00
			633620	77.00	77.00	0.00	0.01	0.01	1.00	5.00	2.00
			633621	77.00	77.90	0.90	1.07	0.24	7.00	5.00	4.46

Selwyn Project Diamond Drill Log

Hole Number:
XYC-217

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		- GREY CHERT FACIES: Consists of laminated medium light grey to medium dark grey chert. Mineralization: 95-99% quartz and up to 5% secondary calcite. - WHITISH GREY ZN-PB MUDSTONE FACIES: Is a laminated cherty rock containing up to 70% sulphides. Mineralization: quartz, sphalerite and galena are the major minerals with only minor amounts of pyrite and locally calcite. Sedimentary diagenetic structures are common and well displayed in the facies, such as: lamination, pseudo-beds, calcite nodules & limestone nodules and abundant water escape structures. Most obvious structure in facies is cross-cutting veins containing massive sphalerite and galena with minor pyrite. They range in width from 0.5 to 10mm. - THIN BEDDED CHERTY MUDSTONE FACIES: Consists of rhythmic intercalated laminae of chert, carbonaceous mudstone and minor micrite. This facies contains significant amounts of Zn and Pb sulphides. - CHERTY MUDSTONE FACIES: Consists of a greyish black monotonous siliceous, carbonaceous mudstone. It is most typically found overlying the thin bedded calcareous mudstone facies. - THIN BEDDED CALCAREOUS MUDSTONE FACIES: Consists of laminated carbonaceous mudstone containing 20-40% calcite, 40-55% quartz and 10-20% muscovite. Sulphides occur in laminae. In the XY area it is usually the lowest facies in the section to contain laminated sulphides. - CALCAREOUS MUDSTONE FACIES: Consists of grey to greyish black monotonous, calcareous siliceous carbonaceous mudstone. There are no feathery calcite beds or pyrite-calcite blebs in the facies, making it easily distinguishable from the CCMS. - GRADED LIMESTONE FACIES: Is a laminated argillaceous limestone with intercalated carbonaceous limestone laminae. The main rock type in the facies									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-217

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		is laminated limestone with laminae up to 0.1-7mm thick. - LIGHT GREY BASAL LIMESTONE FACIES - LGLS: Consists of laminated argillaceous limestone. In the Anniv area it marks the end of the ACTM. It's not always present in the stratigraphy. - BASAL FACIES: This is a highly contorted and locally foliated carbonaceous mudstone. Unlike the other facies it is not repeated higher in the member. It appears locally to contain the slip zone of a major slump. The facies has only been observed in the YX area. It is 0.1-2m thick. The facies consists of massive carbonaceous siliceous mudstone with lenses and laminae of contorted, slightly carbonaceous chert. « 63.90- 77.90 Terrible core recovery, ~20% throughout due to driller error. Recovered competent segments and fragments are largely rounded and reworked by repetitive drilling process. Visible core is largely medium to very high grade. Samples appear much larger (longer) than they are due to low TCR.» « 63.90- 64.90 Light grey silicious mudstone with medium-to-high grade mineralization (10-30%), with medium grey weakly calcareous laminated mudstone, weakly-moderately mineralized (3-10%). Light grey component shows classic "High grade" appearance. Laminated but with secondary fabric infilled by galena/sphalerite. Galena and sphalerite nodules/veinlets observed in high grade light grey pieces. Extremely poor core recovery, available core broken up. True thickness of this range is an estimate because of core loss. » « 64.90- 65.90 ~ 30% core recovery. Very broken-up, fault breccia sized fragments mechanically created. Primarily unlaminated weakly mineralized dark-grey mudstone with some fragments of higher-grade material, possibly out of place. » « 65.90- 66.40 ~50% core recovery. Primarily classic light-grey, high-grade ACTM with brecciated fabric. Abundant visible SPH/GAL nodules and									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-217

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		laminations cross cut by secondary fabric. Very broken up. Generally high-grade mineralization. » « 66.40- 67.80 ~30% core recovery. Primarily dark-grey, weakly to moderately mineralized laminated mudstone, but with one small 15cm segment of light grey, high-grade material. Impossible to estimate true thickness of the high grade component. Extremely broken-up throughout, mainly consisting of smaller fragments. » « 67.80- 69.10 30% recovery. Light-grey unlaminated limestone. No visible mineralization. » « 69.10- 72.40 10% recovery. Core available consists of largely unlaminated silicious, dark-grey mudstone with no visible mineralization. Totally broken up. » « 72.40- 76.00 ~30% recovery. Primarily light-grey limestone, heavily veined (calcite) with minor dark-grey calcareous mudstone. Totally re-worked and broken up. No visible mineralization. » « 76.00- 76.40 Almost 100% calcite vein. » « 76.40- 77.00 Limestone with abundant calcite veining. Totally broken up and reworked. ~45% recovery. » « 77.00- 77.90 Dark-grey weakly calcareous mudstone with minor light grey limestone. Includes a 9cm segment of higher grade silicious mudstone. ~50% recovery. »									
77.90	102.40	CCMS	633622	77.90	79.20	1.30	0.04	0.21	1.00	5.00	0.19
		CCMS – Calcareous Mudstone	633623	79.20	79.20	0.00	6.24	6.83	69.00	180.00	0.91
		Massive, calcareous, carbonaceous, dark grey mudstone. Most of the member is massive, but rare poorly defined bedding and pyrite-calcite micro-concretions are present. Most diagnostic structures are feathery calcite beds (=thin calcite-cemented concretions, many of them contain pyrite cores) and calcite									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-217

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		<i>pseudo-beds (= fibrous calcite vein parallel to bedding).</i> « <i>lm ca 5.00-10.00mm</i> », « <i>nodules py -3.00% 2.00-20.00mm</i> » « <i>77.90- 102.40 Typical CCMS, mudstone very calcareous throughout.</i> » « <i>85.80- 94.70 Massive, carbonaceous fault zone. Flt »« Flt gg 80%»« Flt bx 20%»</i> « <i>@ 95.10 S0 defined by parallel ~1mm thick lenticular pyrite nodules, a la PSMS. S0 tca 25°</i> »									
102.40	104.10	FLT									
		« <i>102.40- 104.10 While this fault is thinner than the huge one above, it is at this fault where we see the unit change between shortened CCMS and TRAN. Much of the displacement, however, may have occurred in the larger fault zone within CCMS, above. FLT</i> » <i>The first 10cm contains: « Flt gg 10%»« Flt bx 90%» After that we see a brecciated section of 1.6m long, rich in quartz/calcite veins.</i>									
104.10	111.80	TRAN									
		<i>TRAN – Transition Formation</i> <i>Consists of laminated tan mudstone and minor intercalated light grey limestone.</i> « <i>lm mdst 1.00-10.00mm</i> » « <i>104.10- 111.80 Primarily non-to-weakly calcareous, medium-grey mudstone with abundant rounded "clasts" of light grey limestone, approximately 20% of rock volume. Multiple sets of very heavy calcite veining throughout unit. Transitional formation is often observed with this appearance and composition, but can be quite different as well. Note that absent here are the thin, sinuous laminations often observed in great abundance normally.</i> »									

Diamond Drill Log

Comprehensive Report for Hole:

XYC-216

Hole No.: XYC-216	Depth: 218.00 m	Horizontal Length: 0.00 m	Project: 1710
Location Data:			
Property:	Selwyn Project	Claim Name:	X 14
Mining District:	Selwyn Basin	Grant Number:	Y 64539
Province/Territory:	Yukon		
UTM Co-Ordinates & Altitude of Drill Hole Collar:			
UTM Easting:	488967.72 m	True Azimuth:	210.0 °
UTM Northing:	6926197.59 m	Hole Angle:	-68.0 °
Elevation (m):	1608.47 m	NTS Name:	Placer Creek
		NTS Number:	105L06
Grid Co-Ordinates of Drill Hole Collar:			
Grid Easting (m):	0.00 m	Grid Name:	HP 06
Grid Northing (m):	0.00 m	Grid Type:	100m
Grid Azimuth:	270.0 °		
Dimond Drilling Contract:			
Drilled By:	CY-01	Date Drilling Start:	09/26/2010
		Date Finish:	10/02/2010
Diamond Drill Core:			
Logged By:	Graham Leroux / Kate	Date Logging Start:	10/09/2010
		Date Finish:	10/13/2010
Legend for Core Logging Codes: PAX			
Core Size:	NQ	Cemented:	Yes
Casing Depth:	9.60 m	Casing Pulled:	Yes
Water Depth:	0.00 m	Overburden Depth:	9.60 m
Level:	Section:	Drift:	

Selwyn Project

Diamond Drill Log

Survey Data for Hole

XYC-216

Hole Comments:

Mon, Sep 27 --- XYC-211 got shut down yesterday. They moved onto target #5. Right now XYC-116 is at a total depth of 51m. The casing is 9.1m deep. The core is still at the drill, no geologist has seen it so far.

=====

Tue, Sep 28 --- At a depth of 113m. In ACTM. I wasn't able yet to locate the USMS-ACTM contact as everything was covered in snow. Visible galena blebs at 109.7m and 110.7m.

=====

Wed, Sep 29 --- At a total depth of 135m. Not sure in which unit it is, as we didn't receive the core yet and David is up at Cantung. Note that the target depth got changed from 125m to 200m, so they will keep on drilling. The Cyr crew is experiencing some difficulties with the hole. Todd told me they will cement the last 10m or so and then drill through the cement in order to get through some bad ground.

=====

Thu, Sep 30 --- Still struggling with the fault (cavity?) in the rock. They tried cementing the fault, but all cement disappeared. They have used bentonite and pellets to close off the fault, but no luck either. They will keep on trying and we will re-evaluate after another 24hr of trying what to do with the hole, as we hit ACTM around 110m and we might be out of it already.

=====

Fri, Oct 01 --- Past the fault now. They drilled yesterday and last night. Still in ACTM!

=====

Sat, Oct 02 --- 18m got drilled in the past 24hrs and during the very beginning of today's dayshift. ACTM was intersected between 86m and 168m. Right now in CCMS. The drill will keep on drilling as Ken is busy moving NL-02. Possibly a move later today, if not today, tomorrow morning.

=====

Sun, Oct 03 --- The drill got shut down, last flexit test was done and the hole got cemented. The drill got moved to target #4.

<i>Depth</i>	<i>Dip</i>	<i>Azimuth</i>
0.00	-68.0	210.0

Selwyn Project Diamond Drill Log

Hole Number:
XYC-216

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
0.00	9.60	OVBR									
9.60	27.80	FLMD									
FLMD – Flaggy Mudstone Formation											
Dark grey mudstone in the upper portions of the unit grading into light grey mudstone to siltstone. Contains abundant wispy bioturbation which ranges from randomly-oriented at the top of the unit to bedding-parallel throughout the majority of the unit. Darker upper section has a strong fetid odour along broken surfaces. « btrb 0.10-2.00cm », « cg xtl crns ca 1.00-5.00% 5.00-150.00cm », « crns py 1.00-5.00% 0.10-0.50mm », « 9.60- 22.90 Typical flaggy textures, heavily bioturbated, pyrite blebs with rims of calcite. Bioturbations roughly follow S0. Graptolitic horizons occur in the upper part of interval and cross the trend of bioturbation. Disseminated pyrite concentrates in some ziones up to 15-20cm thick, pyrite may reach massive state, often associated with calcite. Many stylolites are remineralized by calcite and minor quartz.» « @ 13.30 defined by pyrite pseudobeds S0, tca 45° » « 22.90- 27.80 Very poor recovery over this interval, the broken core pieces are nearly developed into gouge (or are reconstituted gouge already), they are intently affected by faulting and are mylonitic with numerous veinlets remineralized in random orientatio0n . This fault has a mix of FLMD and USMS near the bottom of interval FLT »« gg 15%»« bx 15%»« Brco 70%»											
27.80	86.00	USMS	633151	29.70	30.50	0.80	0.03	0.08	1.00	5.00	0.38
USMS – Upper Siliceous Mudstone			633152	30.50	31.00	0.50	0.39	7.04	8.00	190.00	0.06
Consists of interlaminated dark grey to black mudstone and light to medium grey chert. Regionally, a 1m thick graptolite zone occurs 15m below the top of the upper unit, this is usable as a horizon. The USMS is divided into 3 units. The Lower Unit contains abundant limestone concretions and Galena and sphalerite micro-concretions occur locally near the base of this unit. « gra , lm chrt			633153	31.00	31.20	0.20	0.16	2.13	4.00	60.00	0.08
			633154	31.20	32.00	0.80	0.01	0.20	1.00	5.00	0.05
			633155	83.00	85.10	2.10	0.01	0.32	1.00	10.00	0.03
			633156	85.10	86.00	0.90	0.01	0.18	1.00	5.00	0.06

Selwyn Project Diamond Drill Log

Hole Number:
XYC-216

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		-20.00% » , « cg xtl sph crns ca 5.00-20.00cm » , « bed chrt 10.00-15.00% » , « 27.80- 29.70 Black to greyish black monotonous, carbonaceous, slightly calcareous mudstone. 2-10mm rounded , sparsly spaced pyrite 'concretions' are scattered. Lower part of interval has a 30cm thick muddy limestone 'concretion' that is surrounded by plane parallel failure, pseudotachylite and slick-n-lines associated with some <3mm zones or gouge. » « 29.70- 30.50 Abundant plane-parallel slippage, core still mostly in tact but highly fractured with pseudotachylite + slick-n-lines. FLT »« gg 5%»« bx 5%»« Brco 90%» [Pb: 0.085%; Zn: 0.088%] « 30.50- 31.00 Faulted in interval of ore rock. Laminated mudstone, abundant soft sediment deformation features. Two stages of calcite-quartz veining. Fairly calcareous. Sphalerite is enriched in laminae. [Pb: 1.03%; Zn: 6.11%] » « 31.00- 31.20 Lower part of the fault that brought in the mineralized section, abundant pseudotachylite and slick-n-lines on such surfaces FLT»« gg 50%» « bx 50%»«Brco» «[Pb: 0.222%; Zn: 0.134%] » « 31.20- 32.00 Laminated carbonaceous mudstone with contorted calcic and cherty laminae, 1-3mm pyritic blebs, some of twhich are squiggly. Calcite is often rimmed around coarser pyrite crystals» «[Zn: 0.100%]» « 32.00- 42.90 Carbonaceous mudstone, typical USM S with contorted laminae of cherty and calcic composition. Intercalated with limestone 'concretions' ranging in size from 2cm to >30cm. Often irregular calcite-quartz veins are associated with massive brecciated pyrite and mudstone.» « 42.90- 43.70 increased failure along stylolite seams in Brco FLT »« gg 70%»« bx 15%»« Brco 15%»									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-216

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		« 43.70- 75.10 Typical USMS as described, many limestone 'concretions' are graded and laminated. especially the larger ones. Smaller 'concretions' of limestone are typically massive. Lots of squiggly, discontinuous pyrite blebs. S0 is heavily contorted which compromises core S0 measurements, nonetheless, where consistency exists I have managed to get measurements. Abundant soft sediment deformation, calcite veinlets and calcic fragments. Also large clasts 30-40cm of laminated calcareous mudstone deform carbonaceous mudstone (drop stone?). Many to most of the fracture surfaces express slick-n-lines clearly and well developed in the absence of a defined fault zone. Therefore, internal plane-parallel slippage is significant throughout this unit. » ◁ @ 50.40 defined by regular laminae S0, tca 50° ▷ ◁ @ 61.60 defined by cherty laminae S0, tca 78° ▷ ◁ @ 63.50 defined by calcic laminae S0, tca 80° ▷ « 75.10- 76.50 Abundant well developed slick-n-lines along broken core fractures, remineralized quartz-calcite. FLT» « gg 15%»« bx 10%»« Brco 75%» « 76.50- 83.00 Carbonaceous, slightly calcareous mudstone with contorted cherty + calcic laminae. Calcite veins up to 30cm thick, some have voids with titanite crystals. » « 83.00- 85.10 In typical USMS as described, shoulder sample. Some blocky ground. »«[Zn: 0.225%]» « 85.10- 86.00 Blocky USMS, as described. »«[Zn: 0.160%]»									
86.00	114.00	ACTM	633157	86.00	86.70	0.70	1.33	6.86	4.00	270.00	0.19
ACTM – Active Member			633158	86.70	87.30	0.60	3.59	18.30	8.00	700.00	0.20
			633159	87.30	88.30	1.00	6.05	24.36	5.00	1400.00	0.25
The ACTM consists of a repetitive, possibly rhythmic, sequence of intercalated			633160	88.30	88.90	0.60	2.27	7.07	3.00	240.00	0.32

Selwyn Project Diamond Drill Log

Hole Number:
XYC-216

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
<i>carbonaceous mudstone, cherty mudstone, chert and limestone and locally contains economically significant Zn and Pb sulphides (see bold marked facies), mainly in its sections with well developed lamination. Because of its heterogeneity, the member is distinctive and easily identified.</i> ===== <i>The ACTM has 8 different facies:</i> ===== - GREY CHERT FACIES: <i>Consists of laminated medium light grey to medium dark grey chert. Mineralization: 95-99% quartz and up to 5% secondary calcite.</i> - WHITISH GREY ZN-PB MUDSTONE FACIES: <i>Is a laminated cherty rock containing up to 70% sulphides. Mineralization: quartz, sphalerite and galena are the major minerals with only minor amounts of pyrite and locally calcite. Sedimentary diagenetic structures are common and well displayed in the facies, such as: lamination, pseudo-beds, calcite nodules & limestone nodules and abundant water escape structures. Most obvious structure in facies is cross-cutting veins containing massive sphalerite and galena with minor pyrite. They range in width from 0.5 to 10mm.</i> - THIN BEDDED CHERTY MUDSTONE FACIES: <i>Consists of rhythmic intercalated laminae of chert, carbonaceous mudstone and minor micrite. This facies contains significant amounts of Zn and Pb sulphides.</i> - CHERTY MUDSTONE FACIES: <i>Consists of a greyish black monotonous siliceous, carbonaceous mudstone. It is most typically found overlying the thin bedded calcareous mudstone facies.</i> - THIN BEDDED CALCAREOUS MUDSTONE FACIES: <i>Consists of laminated carbonaceous mudstone containing 20-40% calcite, 40-55% quartz and 10-20% muscovite. Sulphides occur in laminae. In the XY area it is usually the lowest facies in the section to contain laminated sulphides.</i>			633161	88.30	88.90	0.60	2.00	5.33	3.00	170.00	0.38
			633162	88.90	89.70	0.80	1.07	1.35	1.00	40.00	0.79
			633163	89.70	90.60	0.90	0.43	4.25	1.00	130.00	0.10
			633164	90.60	91.60	1.00	0.78	3.55	1.00	110.00	0.22
			633165	91.60	92.10	0.50	0.54	1.33	1.00	40.00	0.41
			633166	92.10	92.90	0.80	1.04	4.40	1.00	120.00	0.24
			633167	92.90	94.10	1.20	1.06	4.13	1.00	130.00	0.26
			633168	94.10	94.70	0.60	0.42	2.86	1.00	80.00	0.15
			633169	94.70	95.30	0.60	2.50	6.56	1.00	180.00	0.38
			633170	95.30	95.30	0.00	0.01	0.01	1.00	5.00	2.00
			633171	95.30	96.20	0.90	0.44	2.85	1.00	80.00	0.15
			633172	96.20	96.80	0.60	3.83	5.42	1.00	250.00	0.71
			633173	96.80	97.90	1.10	13.16	18.85	4.00	1070.00	0.70
			633174	97.90	98.60	0.70	0.40	0.74	1.00	20.00	0.54
			633175	98.60	99.80	1.20	0.15	0.33	1.00	10.00	0.45
			633176	99.80	100.40	0.60	0.56	1.49	1.00	60.00	0.38
			633177	100.40	100.90	0.50	0.10	0.67	1.00	10.00	0.15
			633178	100.90	101.60	0.70	0.04	0.36	1.00	5.00	0.11
			633179	101.60	102.90	1.30	0.03	0.17	1.00	5.00	0.18
			633180	102.90	102.90	0.00	1.41	4.28	25.00	270.00	0.33
			633181	102.90	103.70	0.80	11.82	13.33	4.00	720.00	0.89
			633182	103.70	104.30	0.60	0.67	1.30	1.00	60.00	0.52
			633183	104.30	105.70	1.40	0.04	0.03	1.00	5.00	1.33
			633184	105.70	107.00	1.30	0.07	0.13	1.00	5.00	0.54
			633185	107.00	107.80	0.80	0.47	0.57	1.00	20.00	0.82
			633186	107.80	108.50	0.70	0.13	0.63	1.00	20.00	0.21
			633187	108.50	109.00	0.50	0.43	0.50	1.00	10.00	0.86
			633188	109.00	110.00	1.00	0.84	0.51	1.00	10.00	1.65
			633189	110.00	110.70	0.70	0.01	0.01	1.00	5.00	1.00
			633190	110.70	111.10	0.40	7.05	0.02	11.00	5.00	352.5
			633191	110.70	111.10	0.40	0.03	0.02	1.00	5.00	1.50
			633192	111.10	111.50	0.40	0.01	0.01	1.00	5.00	2.00
			633193	111.50	112.80	1.30	0.01	0.01	1.00	5.00	2.00

Selwyn Project Diamond Drill Log

Hole Number:
XYC-216

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		- CALCAREOUS MUDSTONE FACIES: Consists of grey to greyish black monotonous, calcareous siliceous carbonaceous mudstone. There are no feathery calcite beds or pyrite-calcite blebs in the facies, making it easily distinguishable from the CCMS. - GRADED LIMESTONE FACIES: Is a laminated argillaceous limestone with intercalated carbonaceous limestone laminae. The main rock type in the facies is laminated limestone with laminae up to 0.1-7mm thick. - LIGHT GREY BASAL LIMESTONE FACIES - LGLS: Consists of laminated argillaceous limestone. In the Anniv area it marks the end of the ACTM. It's not always present in the stratigraphy. - BASAL FACIES: This is a highly contorted and locally foliated carbonaceous mudstone. Unlike the other facies it is not repeated higher in the member. It appears locally to contain the slip zone of a major slump. The facies has only been observed in the YX area. It is 0.1-2m thick. The facies consists of massive carbonaceous siliceous mudstone with lenses and laminae of contorted, slightly carbonaceous chert. « 86.00- 86.70 finely laminated mudstone of the ACTM. Erosional cross-bedding, sphalerite-rich laminae and remobilized galena slightly orthogonal to S0. Pyritic laminae can be coarse-grained FLT »« gg 33%»« bx 33%»« Brco 33%» «[Pb: 1.11%; Zn: 2.59%]» « 86.70- 87.30 Very finely laminated mudstone, medium to dark grey-brown. Recrystallized pyrite and quartz in veinlets. Sphalerite enriches as brownish laminae. Galena occurs mostly in veins and is relatively coarse grained, but it also enriches some sphalerite laminae and is vfg »«[Pb: 9.52%; Zn: 15.58%]» « 87.30- 88.30 Light grey to dirty yellow in colour, highly mineralized sphalerite laminae are completely broken up by galena veins. Galena is	633194	112.80	114.00	1.20	0.01	0.18	1.00	5.00	0.06

Selwyn Project Diamond Drill Log

Hole Number:
XYC-216

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		typically coarse grained in the veins. Also pyrite blebs occur with calcite + quartz. Galena tends to remineralize soft-sed slumping planes » «[Pb: 27.6%; Zn: 38.19%]»									
		« 88.30- 88.90 Medium grey finely laminaed mudstone, broken pyrite laminae occur with quartz. <10cm di. limestone 'concretions'. Calcite and quartz veins are often conformable to S0, even though S0 is highly variable and wavy. Sphalerite mineralizes as laminae, galena again is remobilized. »«[Pb: 1.84%; Zn: 5.01%]»									
		« 88.90- 89.70 Dark grey to black laminated, carbonaceous mudstone. Systematic plane-parallel fractures document slippage has occurred. Contorted calcite + minor quartz veins often host broken up massive pyrite. Minor cherty bands »«[Pb: 0.477%; Zn: 0.568%; Ni: 0.108%]»									
		« 89.70- 90.60 Intercalated laminated mudstone and carbonate 'concretions' >50cm di. Most of interval is limestone with recrystallized calcite and quartz veins . Only upper 6cm is laminated muds of the ACTM »«[Pb: 0.483%; Zn: 2.57%]»									
		« 90.60- 91.60 Intercalated medium to dark grey laminated mudstone, high-grade sphalerite laminae, limestone 'concretions' 10-15cm di. Abundant calcite veining, often remineralized stylolites, also blebs of coarse pyrite with calcite. Mudstone parts are slightly-weakly calcareous»«[Pb: 1.05%; Zn: 2.87%]»									
		« 91.60- 92.10 Very calcareous laminated mudstone. Some carbonaceous laminae, but mostly medium grey calcic laminae with intermittent yellowish brown sphalerite laminae. S0 is heavily folded in a syn-depositional style. Limestone 'concretions' 3-10cm di, thin wispy calcite veinlets. Disseminated pyrite is patchy »«[Pb: 0.343%; Zn: 1.33%]»									
		« 92.10- 92.90 Intercalated calcareous light grey laminated mudstone and slightly calcareous dark grey laminated mudstone. 1-2cm limestone concretions. Pyritic laminae is darker mudstone along with sphalerite enriched									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-216

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		laminae. Galena is relatively coarse grained and is remobilized in veinlets. Zones of massive pyrite are often broken up in calcite - quartz veins »«[Pb: 1.23%; Zn: 2.15%]» « 92.90- 94.10 Weakly calcareous, cherty medium to light grey finely laminated mudstone. Limestone 'concretions' 2-10cm di. Calcite veins , only one stage evident. Sphalerite enriches in laminae (depositional) and galena forms blebs up to 2cm long, and is commonly remobilized along soft sed slump planes.»«[Pb: 1.04%; Zn: 3.11%]» « 94.10- 94.70 Muddy laminated limestone intercalated with <10cm thick sections of sphalerite-rich calcareous mudstone laminae. Cuspate stylolites are not later infilled by calcite. Majority of remineralization occurs in mudstone. »«[Pb: 0.699%; Zn: 3.18%]» « 94.70- 95.30 Calcareous mudstone intercalated with limestone 'concretions', weakly laminated. Galena is again remobilized in veins with similar geometry to calcite veins. Sphalerite concentrations in mudstone laminae at the bottom of interval.» «[Pb: 1.19%; Zn: 4.20%]» « 95.30- 96.20 Laminated mudstone, moderately calcareous. Abundant limestone 'concretions' from 0.3-15cm di. Galena veins near base of interval up to 4mm thick and relatively coarse grained. Laminae are deformed by 'concretions' --> maybe they are actually clasts(?) » «[Pb: 1.48%; Zn: 1.96%]» « 96.20- 96.80 Intercalated siliceous, cherty light grey, moderatley-weakly calcareous mudstone, abundant pyrituc laminae enriched with sphalerite causing yellowish-brown colour. Sphalerite also replaces square and cuspate stylolites with poorly laminated medium grey calcareous mudstone, rounded calcite fragments deform laminae »«[Pb: 4.71%; Zn: 3.30%]» < @ 96.20 defined by mineralized laminae S0, tca 40° > « 96.80- 97.90 Light grey laminated galena and sphalerite with abundant									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-216

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		calcite laminae. Disturbed laminae appear bioturbated. »«[Pb: 67.79%; Zn: 29.93%]» Inflated result. < @ 97.70 defined by sphalerite and galena laminae S0, tca 48° > « 97.90- 98.60 Medium to dark grey laminated calcareous mudstone, thick calcite-veins up to 2-3cm. Truncated depositional layers give cross-bedded appearance with high angle difference. Minor pyritic blebs occur with quartz »«[Pb: 0.27%; Zn: 0.52%]» « 98.60- 99.80 Medium grey laminated calcareous mudstone. Often pyritic at depositional boundaries. Also muddy laminated limestone. »«[Pb: 0.117%]» « 99.80- 100.40 Medium grey calcareous laminated mudstone. Voided calcite veins host euhedral titanite crystals. 4cm sections of Light grey laminated galena and sphalerite with abundant calcite laminae. »«[Pb: 0.64%; Zn: 0.971%; Ti: 2.20%]» « 100.40- 100.90 Slightly calcareous dark grey laminated mudstone with limestone laminae near the upper interval. Square and cusped stylolites are numerous and intersect at orthogonal angles.»«[Pb: 0.294%; Zn: 0.580%; W: 0.249%]» « 100.90- 101.60 Med-grey calcareous laminated mudstone, brownish laminae near bottom of interval. Systematic calcite veinlets cut orthogonal to depositional truncated laminae.»«[Zn: 0.473%]» « 101.60- 102.90 Med-grey calcareous laminated mudstone, brownish laminae near bottom of interval. Systematic calcite veinlets cut orthogonal to depositional truncated laminae.»«[Pb: 0.093%; Zn: 0.211%]»» « 102.90- 103.70 Light grey laminated galena and sphalerite with abundant calcite laminae. Disturbed laminae appear bioturbated. »«[Pb: 70.50%; Zn: 25.90%]» Inflated result.»									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-216

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		« 103.70- 104.30 Laminated calcareous med-dark grey mudstone, appears bioturbated along S0, but could also be remobilized soft seds. Abundant squiggly planes of calcite cut across variable S0»«[Pb: 1.550%; Zn: 1.58%]» « 104.30- 105.70 Medium grey laminated, fine grained. Contorted laminae. Rounded limesonte'concretions' of a slightly coarser grain than host limestone. Calcite remineralized stylolites cross-cut laminae. LAtter stage calcite veins have minor quartz and infill fractures.»«[Pb: 0.147%; Zn: 0.073%]» « 105.70- 107.00 Slightly carbonaceous dark grey to black mudstone. Soft sed deformation laminae. Frine-grained limestone 'concretions' contort the surrounding laminae. 'Concretions' of limestone range from 0.2 to >10cm di.»«[Pb: 0.133%; Zn: 0.087%]» « 107.00- 107.80 Finely laminated muddy fine grained limestone. Upper part of the interval (8cm) has a few sphalerite rich bands. No visible galena. Systematic calcite veinlets cross-cut contorted and truncated laminae»«[Pb: 0.133%; Zn: 0.441%]» « 107.80- 108.50 Cross-laminated slightly calcareous mudstone. Systematic stylolites are orthogonal to S0, and seem to occur along brittle failure planes, they are not remineralized.»«[Pb: 0.163%; Zn: 0.316%]» « 108.50- 109.00 Cross0laminated slightly calcareous mudstone intercalated with minor fine-grained limestone. Abundant stylolites. Stylolites are mud-filled and may have galena in them in trace amounts ; however difficult to see.»«[Pb: 0.223%; Zn: 0.322%]» « 109.00- 110.00 Intercalated medium grey and dark grey calcareous laminated to massive mudsonte. Laminated limestone 'concretions' are >15cm di. and deform mudstone laminae around them. Calcite veining has a greter affinity to be close to limestone clasts.» «[Pb: 0.485%; Zn: 0.392%]»									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-216

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
« 110.00- 110.70 Intercalated medium grey and dark grey calcareous laminated to massive mudstone. Laminated limestone 'concretions' are >15cm di. and deform mudstone laminae around them. Calcite veining has a greater affinity to be close to limestone clasts. In addition there are angular limestone clasts and cherty pebbles on some laminae.»«[Pb: 0.485%; Zn: 0.392%]»											
« 110.70- 111.10 Carbonaceous and calcareous dk-grey laminated mudstone with rounded limestone concretions and secondary calcite infilling this plane-parallel fractures (<2mm thick) »«[Pb: 0.149%]»											
« 111.10- 111.50 Recrystallized quartz-calcite vein. Some quartz has been brecciated in calcite matrix.» [Barren]											
« 111.50- 112.80 Carbonaceous, siliceous, slightly calcareous poorly laminated dark grey mudstone, wormy calcic and cherty bands - looks like USMS Rounded limestone fragments deform weakly defined laminae. Remineralized calcite irregular stylolites. »«[Zn: 0.042%]»											
« 112.80- 114.00 Carbonaceous, siliceous, slightly calcareous poorly laminated dark grey mudstone, wormy calcic and cherty bands - looks like USMS Rounded limestone fragments deform weakly defined laminae. Remineralized calcite irregular stylolites. In addition there are 1-5mm pyritic blebs and discontinuous squiggly pyrite wisps. »«[Zn: 0.111%]»											
114.00	118.10	FLT	633195	114.00	116.10	2.10	0.01	0.11	1.00	5.00	0.09
« FLT »« gg 10%»« bx 15%»« Brco 75%»			633196	116.10	118.10	2.00	0.06	0.52	1.00	10.00	0.12
« 114.00- 116.10 Poor recovery over this interval of carbonaceous and cherty, poorly laminated mudstone. Abundant plane-parallel slippage has occurred and developed pseudotachylite with slick-n-lines.» «[Zn: 0.081%]»											
« 116.10- 118.10 Poor recovery over this interval of carbonaceous and cherty, poorly laminated mudstone. Abundant plane-parallel slippage has occurred and developed pseudotachylite with slick-n-lines. In addition this unit											

Selwyn Project Diamond Drill Log

Hole Number:
XYC-216

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		looks like USMS» «[Pb: 0.055%; Zn: 0.369%]»									
118.10	131.70	USMS	633197	118.10	119.60	1.50	0.01	0.27	1.00	5.00	0.04
<i>USMS – Upper Siliceous Mudstone</i>			633198	119.60	121.00	1.40	0.01	0.28	1.00	5.00	0.04
<i>Consists of interlaminated dark grey to black mudstone and light to medium grey chert. Regionally, a 1m thick graptolite zone occurs 15m below the top of the upper unit, this is usable as a horizon. The USMS is divided into 3 units. The Lower Unit contains abundant limestone concretions and Galena and sphalerite micro-concretions occur locally near the base of this unit. « gra , lm chrt -20.00% » , « cg xtl sph crns ca 5.00-20.00cm » , « bed chrt 10.00-15.00% » ,</i> <i>« 118.10- 119.60 Typical USMS, dark grey to black laminated muddstone, calcic and cherty bands, stretched out rounded limestone fragments associated with calcite veining. »«[Zn: 0.23%]»</i> <i>« 119.60- 121.00 USMS as described, upper 20cm of interval has limestone fragments > 10cm di and abundant quartz veining around them »«[Zn: 0.249%]»</i> <i>« 121.00- 122.10 Blocky section of USMS as described. In addition there are more calcite veins (~3% of interval) »«[Zn: 0.161%]»</i> <i>« 122.10- 123.60 Laminated limestone, graded, bioturbated at upper part of interval, depositional limestone. »«[Barren]»</i> <i>« 123.60- 124.90 Heavily calcite veined, blocky, graded carbonaceous mudstone. Lower part of interval (10cm) has a laminated limestone fragment with calcite-veins.»«[Pb: 0.087%]»</i> <i>« 124.90- 126.30 Heavily calcite veined, blocky, graded carbonaceous mudstone.»«[Pb: 0.049%; Zn: 0.109%]»</i> <i>« 126.30- 126.80 Graded, laminated limestone with truncated depositional</i>			633199	121.00	122.10	1.10	0.01	0.17	1.00	5.00	0.06
			633200	122.10	122.10	0.00	0.01	0.01	1.00	5.00	2.00
			633201	122.10	123.60	1.50	0.01	0.01	1.00	5.00	2.00
			633202	123.60	124.90	1.30	0.01	0.06	1.00	5.00	0.17
			633203	124.90	126.30	1.40	0.01	0.18	1.00	5.00	0.06
			633204	126.30	126.80	0.50	0.01	0.01	1.00	5.00	2.00
			633205	126.80	128.00	1.20	0.01	0.16	1.00	5.00	0.06
			633206	128.00	130.00	2.00	0.01	0.06	1.00	5.00	0.17
			633207	130.00	131.70	1.70	0.08	0.41	1.00	20.00	0.20

Selwyn Project Diamond Drill Log

Hole Number:
XYC-216

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		layers. »«[Barren]» « 126.80- 128.00 Laminated carbonaceous mudstone with 1-5mm cherty and calcic bands. Also, white calcite bands can be conformable. Massive pyrite layers 1-4mm thick are brecciated by calcite + mudstone. Limestone 'concretions' at base of interval (20cm thick) has sharp serrated boundaries.»«[Pb: 0.049%; Zn: 0.086%]» « 128.00- 131.70 FLT »« gg 10%»« bx 30%»« Brco 60%» « 128.00- 130.00 Typical USMS in carbonaceous fault zone. Increased >5cm recrystallized calcite - quartz veins. »«[Zn: 0.126%]» « 130.00- 131.70 Typical USMS in carbonaceous fault zone. Increased >5cm recrystallized calcite - quartz veins. In addition concentrated laminae 4-8cm thick host massive pyrite. Especially near top of interval.»«[Pb: 0.106%; Zn: 0.444%]»									
131.70	168.20	ACTM	633208	131.70	132.40	0.70	3.77	5.78	3.00	330.00	0.65
		ACTM – Active Member	633209	132.40	133.90	1.50	0.70	3.88	2.00	140.00	0.18
		The ACTM consists of a repetitive, possibly rhythmic, sequence of intercalated carbonaceous mudstone, cherty mudstone, chert and limestone and locally contains economically significant Zn and Pb sulphides (see bold marked facies), mainly in its sections with well developed lamination. Because of its heterogeneity, the member is distinctive and easily identified.	633210	133.90	133.90	0.00	0.91	1.36	220.00	90.00	0.67
			633211	133.90	134.80	0.90	3.40	14.08	3.00	780.00	0.24
			633212	134.80	135.90	1.10	0.81	4.21	2.00	140.00	0.19
			633213	135.90	137.00	1.10	1.11	5.66	1.00	160.00	0.20
			633214	137.00	137.40	0.40	0.14	0.48	1.00	10.00	0.29
			633215	137.40	138.50	1.10	1.77	7.73	2.00	190.00	0.23
			633216	138.50	139.10	0.60	0.18	0.81	1.00	20.00	0.22
		=====	633217	139.10	140.20	1.10	0.15	0.97	1.00	30.00	0.15
		The ACTM has 8 different facies:	633218	140.20	141.00	0.80	0.04	1.37	1.00	40.00	0.03
		=====	633219	141.00	142.40	1.40	0.13	0.34	1.00	5.00	0.38
			633220	142.40	142.80	0.40	1.22	2.45	1.00	70.00	0.50
		- GREY CHERT FACIES: Consists of laminated medium light grey to medium dark grey chert. Mineralization: 95-99% quartz and up to 5% secondary calcite.	633221	142.40	142.80	0.40	1.56	2.23	1.00	60.00	0.70
			633222	142.80	143.40	0.60	0.51	4.13	3.00	110.00	0.12
			633223	143.40	144.40	1.00	2.07	6.84	1.00	210.00	0.30
		- WHITISH GREY ZN-PB MUDSTONE FACIES: Is a laminated cherty rock containing	633224	144.40	145.30	0.90	1.23	4.94	1.00	130.00	0.25

Selwyn Project Diamond Drill Log

Hole Number:
XYC-216

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
up to 70% sulphides. Mineralization: quartz, sphalerite and galena are the major minerals with only minor amounts of pyrite and locally calcite. Sedimentary diagenetic structures are common and well displayed in the facies, such as: lamination, pseudo-beds, calcite nodules & limestone nodules and abundant water escape structures. Most obvious structure in facies is cross-cutting veins containing massive sphalerite and galena with minor pyrite. They range in width from 0.5 to 10mm. - THIN BEDDED CHERTY MUDSTONE FACIES: Consists of rhythmic intercalated laminae of chert, carbonaceous mudstone and minor micrite. This facies contains significant amounts of Zn and Pb sulphides. - CHERTY MUDSTONE FACIES: Consists of a greyish black monotonous siliceous, carbonaceous mudstone. It is most typically found overlying the thin bedded calcareous mudstone facies. - THIN BEDDED CALCAREOUS MUDSTONE FACIES: Consists of laminated carbonaceous mudstone containing 20-40% calcite, 40-55% quartz and 10-20% muscovite. Sulphides occur in laminae. In the XY area it is usually the lowest facies in the section to contain laminated sulphides. - CALCAREOUS MUDSTONE FACIES: Consists of grey to greyish black monotonous, calcareous siliceous carbonaceous mudstone. There are no feathery calcite beds or pyrite-calcite blebs in the facies, making it easily distinguishable from the CCMS. - GRADED LIMESTONE FACIES: Is a laminated argillaceous limestone with intercalated carbonaceous limestone laminae. The main rock type in the facies is laminated limestone with laminae up to 0.1-7mm thick. - LIGHT GREY BASAL LIMESTONE FACIES - LGLS: Consists of laminated argillaceous limestone. In the Anniv area it marks the end of the ACTM. It's not always											
			633225	145.30	146.20	0.90	1.97	6.35	1.00	170.00	0.31
			633226	146.20	146.90	0.70	0.32	2.18	1.00	50.00	0.15
			633227	146.90	147.40	0.50	2.28	11.79	3.00	250.00	0.19
			633228	147.40	148.80	1.40	2.52	8.18	1.00	180.00	0.31
			633229	148.80	149.60	0.80	0.34	0.10	1.00	5.00	3.40
			633230	149.60	149.60	0.00	0.01	0.01	1.00	5.00	1.00
			633231	149.60	150.80	1.20	0.05	0.04	1.00	5.00	1.25
			633232	150.80	151.80	1.00	0.01	0.09	1.00	5.00	0.11
			633233	151.80	152.80	1.00	0.07	0.01	1.00	5.00	14.00
			633234	152.80	153.60	0.80	0.03	0.02	1.00	5.00	1.50
			633235	153.60	154.60	1.00	0.03	0.03	1.00	5.00	1.00
			633236	154.60	155.10	0.50	0.26	1.69	1.00	40.00	0.15
			633237	155.10	155.60	0.50	0.14	1.17	1.00	30.00	0.12
			633238	155.60	156.30	0.70	0.14	2.11	1.00	40.00	0.07
			633239	156.30	156.70	0.40	0.10	0.08	1.00	5.00	1.25
			633240	156.70	156.70	0.00	1.42	4.40	28.00	270.00	0.32
			633241	156.70	157.60	0.90	0.43	2.73	4.00	70.00	0.16
			633242	157.60	158.10	0.50	0.21	1.51	2.00	40.00	0.14
			633243	158.10	159.00	0.90	0.25	1.43	1.00	30.00	0.17
			633244	159.00	159.50	0.50	0.10	0.12	1.00	5.00	0.83
			633245	159.50	160.30	0.80	0.16	1.37	1.00	30.00	0.12
			633246	160.30	162.20	1.90	0.45	0.93	3.00	20.00	0.48
			633247	162.20	163.40	1.20	0.03	1.03	1.00	30.00	0.03
			633248	163.40	164.60	1.20	0.01	0.01	1.00	5.00	2.00
			633249	164.60	165.90	1.30	0.01	0.01	1.00	5.00	2.00
			633250	165.90	166.10	0.20	0.08	0.06	2.00	5.00	1.33
			633251	165.90	166.10	0.20	0.07	0.03	1.00	5.00	2.33
			633252	166.10	167.40	1.30	0.01	0.01	1.00	5.00	2.00
			633253	167.40	168.20	0.80	0.01	0.01	1.00	5.00	2.00

Selwyn Project Diamond Drill Log

Hole Number:
XYC-216

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		present in the stratigraphy. - BASAL FACIES: This is a highly contorted and locally foliated carbonaceous mudstone. Unlike the other facies it is not repeated higher in the member. It appears locally to contain the slip zone of a major slump. The facies has only been observed in the YX area. It is 0.1-2m thick. The facies consists of massive carbonaceous siliceous mudstone with lenses and laminae of contorted, slightly carbonaceous chert. « 131.70- 132.40 Laminated siliceous metaliferous mudstone. ~10% calcareous laminae, ~10% brownish yellow sphalerite-rich laminae, ~50% medium grey muddy laminae. Remobilized galena is coarse grained (~2-3%) and concentrated often as blebs.»«[Pb: 4.18%; Zn: 5.58%]» « 132.40- 133.90 Graded interval, Upper ~15cm is massive limestone mixed with pyrite, mud-rich seams and calcite veins. Next ~20cm is weakly carbonaceous med-grey calcite veinleted siliceous mudstone. Next ~10-15cm is laminaed metaliferous mudstone as described in previous sample.»«[Pb: 0.749%; Zn: 2.92%]» « 133.90- 134.80 Laminated and bioturbated light grey siliceous sulphidic mudstone, intercalated with minor amounts (<5%) of laminated metalliferous mudstone. Galena concentrates with grey mud along trend of bioturbations, it is fine-grained. Siliceous nature is caused by chert laminae which account for ~70% of interval.»«[Pb: 4.2%; Zn: 7.4%]» « 134.80- 135.90 Blocky ground. Pyritic laminae are 2cm thick and massive near upper interval. Med-grey laminated mudstone with wormy calcite, calcic and cherty bands near lower interval.»«[Pb: 0.927%; Zn: 1.72%]» « 135.90- 137.00 Laminated metalliferous mudstone as described, but here mostly brecciated, no strong sign of faulting, only fracturing. »«[Pb: 1.84%; Zn: 4.8%]» « 137.00- 137.40 Laminated med-grey to light-grey limestone with some mud									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-216

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		and sphalerite-rich laminae (<1%). Medium grained limestone. »«[Pb: 0.316%; Zn: 0.538%]»									
		« 137.40- 138.50 Heterogeneous interval. Intercalated and cross laminated metalliferous mudstone, calcic laminae, pyritic laminae, chert laminae in full range of shade from light grey to nearly black. Rounded limestone fragments distort laminae. Recrystallized calcite-quartz veins near bottom. »«[Pb: 1.83%; Zn: 4.25%]»									
		« 138.50- 139.10 Laminated mud-rich limestone intercalated with massive limestone. Calcite veins typically 1-7mm cut orthogonal to S0.»«[Pb: 0.208%; Zn: 0.562%]»									
		« 139.10- 140.20 Dk-grey mud-rich limestone, finely laminated. Flattened pyrite nodules occur with cores of limestone. Med grey laminae and dark grey laminae which are dominant. »«[Pb: 0.192%; Zn: 0.622%]»									
		« 140.20- 141.00 Dark grey weakly laminated and calcareous mudstone. Pyritic laminae ~6mm thick and nodules with calcite rims ~6-10mm di. Remineralized stylolites. Calcite vein swarm near upper interval. »«[Pb: 0.091%; Zn: 0.846%]»									
		« 141.00- 142.40 Massive limestone with some weakly laminated sections. Light grey in colour. Abundant quartz-calcite veins throughout (10-20%) »«[Zn: 0.103%]»									
		« 142.40- 142.80 Muddy limestone intercalated with dark grey carbonaceous mudstone. Mudstone is host to mineralizing sulphides. »«[Pb: 0.995%; Zn: 1.49%]»									
		« 142.80- 143.40 Laminated calcareous mudstone with sphalerite-rich laminae. Abundant limestone fragments (rounded) distort laminae. Brittle and ductile deformation features are seen in calcite veins.»«[Pb: 0.567%; Zn: 2.5%]»									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-216

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		« 143.40- 144.40 Finely interlaminated carbonaceous and calcareous mudstone with light and dark chert and brownish yellow sphalerite. Galena mineralization is coarser grained and overprints structure. Abundant soft sed deformation and rounded limestone clasts. Pyrite is also later stage and coarse grained, often associated with limestone.»«[Pb: 2.38%; Zn: 4.31%]»									
		« 144.40- 145.30 Finely interlaminated carbonaceous and calcareous mudstone with light and dark chert and brownish yellow sphalerite. Galena mineralization is coarser grained and overprints structure. Abundant soft sed deformation and rounded limestone clasts. Pyrite is also later stage and coarse grained, often associated with limestone.»«[Pb: 0.816%; Zn: 2.78%]»									
		« 145.30- 146.20 Intercalated laminated limestone and metalliferous laminated calcareous mudstone. Rounded limestone clasts deform laminae. Galena is fine grained and appears to be interstitial to sphalerite in laminae.»«[Pb: 1.95%; Zn: 3.83%]»									
		« 146.20- 146.90 Intercalated laminated limestone and metalliferous laminated calcareous mudstone. Rounded limestone clasts deform laminae. Galena is fine grained and appears to be interstitial to sphalerite in laminae. In addition there is some fault breccia with slick-n-lines on some pieces (~2-3cm thick blocky zone) »«[Pb: 0.607%; Zn: 2.12%]»									
		« 146.90- 147.40 Laminated mudstone. Intercalated sphalerite-rich laminae to massive zones of sphalerite. Galena concentrates in lighter colour calcareous zones 2-7mcm thick. Abundant soft sed deformation. Recrystallized calcite-quartz veins. »«[Pb: 2.25%; Zn: 5.81%]»									
		« 147.40- 148.80 Medium to dark grey, finely laminated carbonaceous mudstone, weakly calcareous. Laminae are all varibale in S0 and highly wavy. Remobilized sphalerite and galena in discordant veinlets infilling fractures. Galena is coarser-grained.»«[Pb: 1.5%; Zn: 3.7%]»									
		« 148.80- 149.60 Finely laminated mud-rich medium grey limestone. Upper part of interval has pyrite to massive pyrite laminae. Wormy calcite-quartz									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-216

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		veins ~3-6mm wide. »«[Pb: 0.288%; Zn: 0.182%]» « 149.60- 150.80 Finely laminated medium grey limestone, relatively little remineralization. Pyritic laminae 2-6mm thick. Limestone appears to have been brecciated in some places as there are sharp contrasts to the laminae. 10-20cm rounded fragments of limey rock.»«[Pb: 0.106%]» « 150.80- 151.80 Finely laminated medium grey limestone, relatively little remineralization. Pyritic laminae 2-6mm thick. Limestone appears to have been brecciated in some places as there are sharp contrasts to the laminae. 10-20cm rounded fragments of limey rock.»«[Zn: 0.085%]» « 151.80- 152.80 Dark grey to black calcareous and carbonaceous laminated mudstone. Pyritic laminae account for ~3% of interval . rounded laminated limestone clats occur sparsly throughout (1-12cm)di.»«[Pb: 0.198%]» « 152.80- 153.60 Dark grey to black calcareous and carbonaceous laminated mudstone. Pyritic laminae account for ~3% of interval . rounded laminated limestone clats occur sparsly throughout (1-12cm)di. In addition there is a slight increase in calcite veining.»«[Pb: 0.120%; Zn: 0.058%]» « 153.60- 154.60 Blocky ground of intercalated limestone and medium grey calcareous mudstone. Pyritic laminae are broken up often and occur in the mudstone. »«[Pb: 0.245%; Zn: 0.098%]» « 154.60- 155.10 Siliceous highly fractured along stylolite swarms, med0grey to dark grey mudstone. Pyritic nodules throughout (~1-2%). »«[Pb: 0.324%; Zn: 0.446%]» « 155.10- 155.60 Cross-bedded, laminated medium to light grey limestone, intercalated with dark grey to black siliceous mudstone (~5%). Minor pyritic laminae are weak spots where slippage concentrates.»«[Pb: 0.430%; Zn: 1.42%]» « 155.60- 156.30 Irregularly, weakly laminated dark grey siliceous mudstone with calcic bands 4-7mm thick helping to define contorted S0. Pyrite									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-216

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		nodules associated with quartz-calcite, also as blebs up to 5cm across. Abundant calcite remineralized stylolites.»«[Pb: 0.166%; Zn: 1.40%]» « 156.30- 156.70 Massive to weakly laminated limestone with remineralized stylolites, and wispy muddy streaks that appear bioturbated. »«[Pb: 0.160%]» « 156.70- 157.60 Medium grey, laminated calcareous mudstone. Pyrite nudules (<1%) have rims of quartz-calcite typically. Sphalerite is finely disseminated throughout, although does concentrate in some laminae. Rounded limestone clasts have pyrite rims. »«[Pb: 0.624%; Zn: 2.03%]» « 157.60- 158.10 Laminated limestone with minor muddy laminae. Through this interval there are pyrite veins and brecciated layers of pyrtie (10-12%) that are associated with quartz and calcite. »«[Pb: 0.153%; Zn: 1.53%]» « 158.10- 159.00 Laminated muddy limestone. Sphalerite-rich laminae, also calcic and calcite laminae. Pyrite forms in layers as fine clusters <2mm in di. They bunch and form layers and gobs. Remineralized calcite in stylolite swarms.»«[Pb: 0.407%; Zn: 1.10%]» « 159.00- 159.50 Laminated muddy limestone. Sphalerite-rich laminae, also calcic and calcite laminae. Pyrite forms in layers as fine clusters <2mm in di. They bunch and form layers and gobs. Remineralized calcite in stylolite swarms. In addition quartz-calcite veins cut laminae systematically at low angle to S0 »«[Pb: 0.202%; Zn: 0.187%]» « 159.50- 160.30 Slightly calcareous laminated muddy limestone. Sphalerite-rich laminae, also calcic and calcite laminae. Pyrite forms in layers as fine clusters <2mm in di. They bunch and form layers and gobs. »«[Pb: 0.393%; Zn: 1.04%]» « 160.30- 162.20 Massive pyrite nodules up to 15cm di., some brecciated by quartz and calcite. Laminated muddy limestone. Sphalerite-rich laminae, also calcic and calcite laminae. Pyrite forms in layers as fine clusters <2mm in di. They bunch and form layers and gobs. Remineralized calcite in									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-216

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		stylolite swarms. »«[Pb: 0.424%; Zn: 0.625%]» « 162.20- 163.40 Blocky ground. Laminated muddy limestone. Sphalerite-rich laminae, also calcic and calcite laminae. Pyrite forms in layers as fine clusters <2mm in di. They bunch and form layers and gobs. Remineralized calcite in stylolite swarms.»«[Pb: 0.104%; Zn: 0.477%]» « 163.40- 164.60 Bioturbated cherty light grey basal limestone to the ACTM. Abundant pyritic blebs 1-3mm, elongated along S0. Minor limestone clasts. »«[Zn: 0.078%]» « 164.60- 165.90 Massive to weakly laminated light grey fine grained limestone. »«[Barren]» « 165.90- 166.10 Heterogeneous mix of med-dark grey laminated mudstone and limestone with abundant pyrite and calcite veining. Brecciated mudstone in calcite veins and slight bioturbated features in limestone.»«[ZPb: 0.158%]» « 166.10- 167.40 Bioturbated cherty light grey basal limestone to the ACTM. Abundant pyritic blebs 1-3mm, elongated along S0. Minor limestone clasts. »«[Barren]» « 167.40- 168.20 Weakly laminated basal limestone as described, pyrite nodules (1-3mm) di. help define laminae. Rounded limestone clasts (2-6cm). »«[Barren]»									
168.20	218.00	CCMS	633254	168.20	169.50	1.30	0.01	0.14	1.00	5.00	0.07
		CCMS – Calcareous Mudstone Massive, calcareous, carbonaceous, dark grey mudstone. Most of the member is massive, but rare poorly defined bedding and pyrite-calcite micro-concretions are present. Most diagnostic structures are feathery calcite beds (=thin calcite-cemented concretions, many of them contain pyrite cores) and calcite pseudo-beds (= fibrous calcite vein parallel to bedding).									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-216

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		« lm ca 5.00-10.00mm », « nodules py -3.00% 2.00-20.00mm », « 168.20- 169.50 After this interval everything is barren. Carbonaceous and siliceous dark grey mudstone with calcic and cherty bands. Pyritic bands and blebs. » «[Pb: 0.115%; Zn:0.117%]» « 169.50- 180.60 Typical CCMS. Dark grey to black mudstone with thin <2mm wispy calcite veinlets, some minor calcareous sections. Minor plane-parallel slippage. Pyrite associated with calcite -quartz. Calcic and pyritic bands 4-6mm thick.» « 189.60- 190.70 Zone of grey chert banding that looks like USMS. Disseminated pyrite in bands and wisps. » « 192.20- 196.50 zone contains five large calcite veins between 20cm and 50cm wide. » « 204.40- 213.20 Chert banding as at 189.6 and intensified calcite veins. » « 210.60- 211.80 mostly reconstituted gouge and breccia FLT »« gg 70%»« bx 20%»« Brco 10%»									
218.00	218.00	EOH									

Diamond Drill Log

Comprehensive Report for Hole:

XYC-215

Hole No.: XYC-215	Depth: 432.20 m	Horizontal Length: 0.00 m	Project: 1710
Location Data:			
Property:	Selwyn Project	Claim Name:	X 46
Mining District:	Selwyn Basin	Grant Number:	Y 64679
Province/Territory:	Yukon		
UTM Co-Ordinates & Altitude of Drill Hole Collar:			
UTM Easting:	487284.00 m	True Azimuth:	33.0 °
UTM Northing:	6927260.00 m	Hole Angle:	-71.0 °
Elevation (m):	1417.00 m	NTS Name:	Placer Creek
		NTS Number:	105L06
Grid Co-Ordinates of Drill Hole Collar:			
Grid Easting (m):	0.00 m	Grid Name:	HP 06
Grid Northing (m):	0.00 m	Grid Type:	100m
Grid Azimuth:	100.0 °		
Dimond Drilling Contract:			
Drilled By:	NL-03	Date Drilling Start:	09/26/2010
		Date Finish:	10/05/2010
Diamond Drill Core:			
Logged By:	Graham Leroux / Matt	Date Logging Start:	10/10/2010
		Date Finish:	10/19/2010
Legend for Core Logging Codes: PAX			
Core Size:	NQ	Cemented:	Yes
Casing Depth:	5.70 m	Casing Pulled:	Yes
Water Depth:	0.00 m	Overburden Depth:	5.70 m
Level:	Section:	Drift:	

Selwyn Project

Diamond Drill Log

Survey Data for Hole

XYC-215

Hole Comments:

Mon, Sep 27 --- It was decided to abandon XYC-214 at a depth of 247m in USMS due to a stuck core barrel at the bottom of the hole. Only 7 NQ rods and the casing was retrieved from the hole, the other 73 NQ rods were left in the hole. XYC-215 has same azimuth but a dip of 70. It's target #42 in the 'Collar Setups'. The hole was at 103m and in FLMD at morning shift change.

Tue, Sep 28 --- The hole was at a total depth of 149m at morning shift change. Still in FLMD. Pretty broken up.

Wed, Sep 29 --- At a total depth of 231m and in USMS. The FLMD-USMS contact was approximately at 166m. The core is badly broken up.

Thu, Sep 30 --- At a total depth of 274m and still in USMS. The core is very badly broken up, especially between 228m - 256m.

Fri, Oct 01 --- At a total depth of 316m and still in USMS. Drilling is going well. On Wednesday and Thursday we had no dayshift on this drill rig. Today we expect the new day shift crew.

Sat, Oct 02 --- In CCMS at a total depth of 351m. ACTM was intersected from approximately 318.5m to 340.8m. Two sections of roughly 15cm long, one with combined grades of 12% and the other one of 20% were the highlights of the ACTM intersection. Other than that, the ACTM didn't look that great at first sight. The new day crew for this drill is coming in on Wednesday. So, we got 10m of CCMS. We will let the guys drill half of the upcoming night shift and then get ready for a move.

Sun, Oct 03 --- The hole got shut down yesterday. Night shift drilled half of the night, did the last flexit test and cemented the hole from bottom to a depth of 300m. Upon looking at the core that was drilled during last night's shift, a fault was intersected that took us from CCMS back into ACTM. So : 318.5-340.8: ACTM / 340.8-350.2: CCMS / 350.2-357.5: FLT / 357.5-....:ACTM. There is no dayshift, so Matt and I are leaning towards drilling through the cement and continue drilling the ACTM. We spoke to Mark the driller, and he said he can do it. The 14m of ACTM was not the greatest, but it is ACTM nonetheless and the grades could get better deeper down the hole.

Mon, Oct 04 --- Mark was able to put the casing back in the hole and lower the rod string through the existing hole. All cement got drilled out and new footage (26') was drilled. Still in ACTM.

Tue, Oct 05 --- At a total depth of 1418ft, in CCMS, hole to have rods pulled and cemented on tonight's nightshift. ACTM-CCMS contact at 1283ft.

<i>Depth</i>	<i>Dip</i>	<i>Azimuth</i>
0.00	-71.0	33.0
48.20	-71.5	34.4
93.90	-72.3	37.0
139.60	-71.6	36.4

Selwyn Project

Diamond Drill Log

Survey Data for Hole

XYC-215

Selwyn Chihong Mining Ltd.#700-509 Richards Street
Vancouver, British Columbia
Canada V6B 2Z6

185.30	-71.3	39.6
231.00	-72.0	40.8
276.80	-71.7	41.1
322.50	-71.2	42.0
368.20	-71.1	42.2

Selwyn Project Diamond Drill Log

Hole Number:
XYC-215

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
0.00	5.70	OVBR									
5.70	8.60	BSSM <i>BSSM – Backside Siliceous Mudstone</i> <i>Devonian Siliceous Mudstone – Upper Chert Formation</i> <i>Greyish black laminated chert and siliceous mudstone. Randomly-oriented to bedding-parallel bioturbation is common in the bottom of the unit. « lm chrt 75.00-95.00% », « btrb 0.10-2.00cm »</i> <i>« 5.70- 8.60 Medium to light grey, calcareous, laminated mudstone. Pyritic veinlets and recrystallized calcite + quartz veins. Abundant irregular stylolites and stylolite swarms. »</i>									
8.60	22.50	FLT <i>« Flt »« Flt gg 45%»« flt bx 30%»« Brco 25%»</i> <i>« 8.60- 22.50 Fault interval has about equal parts of cherty and silicious, carbonaceous BSSM, massive calcite and quartz veins, and flaggy mudstone. »</i>									
22.50	164.20	FLMD <i>FLMD – Flaggy Mudstone Formation</i> <i>Dark grey mudstone in the upper portions of the unit grading into light grey mudstone to siltstone. Contains abundant wispy bioturbation which ranges from randomly-oriented at the top of the unit to bedding-parallel throughout the majority of the unit. Darker upper section has a strong fetid odour along broken surfaces. « btrb 0.10-2.00cm », « cg xtl crns ca 1.00-5.00% 5.00-150.00cm », « crns py 1.00-5.00% 0.10-0.50mm »</i> <i>« 22.50- 23.10 Broken up along bioturbation trend. Slick-n-lines only weakly developed. Carbonaceous and partially silicious in lower interval. »</i>									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-215

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		« 23.10- 24.20 Recrystallized calcite and quartz in fault zone, commonly re-lithifies breccia fragments Flt »« Flt gg 15%»« Flt bx 35%»« Brco 50%» « 24.20- 27.30 Laminated silicious mudstone, finely laminated, quartz veins and calcite veins. Convolutd S0. Massive brecciated pyrite is a common feature of larger cal-qt veins. Abundant slippage has occured along lamination/ bioturbation place, especially lower in interval. » « 27.30- 28.10 Laminated limestone concretion with cal-qt veins. » « 28.10- 30.30 Medium to dark grey, weakly bioturbated mudstone. Pyrite nodules and blebs. Wispy cal-qt veins. » « 30.30- 31.30 Lots of pyrite in the fault region, ~10-20% Flt »« Flt gg 20%»« Flt bx 75%»« Brco 5%» « 31.30- 48.60 Typical floggy mudstone. Abundant pyrite nodules, up to 5cm di. Recrystallized cal-qt. Bioturbations are not consistent throughout, except in lower part of interval. » « @ 47.30 S0 defined by bioturbations S0 tca 20° » « 48.60- 49.50 Well developed slick-n-lines on broken core surfaces. Flt »« Flt gg 10%»« Flt bx 10%»« Brco 80%» « 49.50- 51.60 Graphitic floggy mudstone, many sections have massive pyrite up to 5-6cm thick. Remineralized stylolites. » « 51.60- 52.70 Increases of recryslalized qt in fault zone. Flt »« Flt gg 15%»« Flt bx 50%»« Brco 35%» « 52.70- 86.10 Typical floggy texture, med-grey, bioturbated, pyrite nodules with calcite +/- quartz veins. S0 is nearly 0 degrees tca in many long									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-215

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		stretches. Calcite-qt veins often parallel the trends in the bioturbations - they also contain pyrite often. » < @ 54.80 S0 defined by bioturbated laminae S0 tca 30° > < @ 61.20 S0 defined by bioturbated laminae S0 tca 25° > < @ 65.50 S0 defined by plane-parallel fracture S0 tca 17° > < @ 70.50 S0 defined by cal-qt veins and laminae S0 tca 12° > < @ 77.90 S0 approaches 0 degrees. S0 tca 0° > « 86.10- 92.70 Gouge on fracture surfaces 2-3mm thick. Failure along bioturbation plane. Flt »« Flt gg 5%»« Flt bx 45%»« Brco 45%» « 92.70- 93.90 Laminated calcareous mudstone, medium grey, abundant randomly oriented qrt-cal veins. Two stage qt-cal veins. » « 93.90- 96.20 Dark grey laminated mudstone, heavily fractured and slightly brecciated. » « 96.20- 96.70 Quartz vein with minor calcite. » « 96.70- 104.20 In typical medium grey flaggy mudstone. Flt »« Flt gg 35%»« Flt bx 50%»« Brco 35%» « 104.20- 108.60 Competent flaggy mudstone, very little qt veining. » « 108.60- 111.90 In medium grey flaggy mudstone. Flt »« Flt gg 30%»« Flt bx 35%»« Brco 35%» « 111.90- 120.70 Medium-grey bioturbated flaggy mudstone, minor faults throughout 5-20cm with some gouge and breccia. » < @ 107.00 S0 defined by bioturbated laminae S0 tca 45° > < @ 114.90 S0 defined by bioturbated laminae S0 tca 45° > < @ 119.80 S0 defined by bioturbated laminae S0 tca 25° >									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-215

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
« 120.70- 129.50 Increases in calcite veining and remineralization in fault region of typical flaggy mudstone. Flt »« Flt gg 25%»« Flt bx 60%»« Brco 15%» « 129.50- 130.20 Region of relatively competent flaggy mudstone with S0 parallel to core axis. » « @ 129.80 S0 defined by wavy bioturbated laminae. S0 tca 0° » « 130.20- 136.10 Abundant micro-calcite veinlets throughout flaggy mudstone. Flt »« Flt gg 40%»« Flt bx 50%»« Brco 10%» « 136.10- 140.20 Intercalated muddy calcareous laminated mudstone, with dark grey pyritic mudstone and medium grey floggy mudstone - again somewhat pyritic. Two stage veining - first stage remineralizes stylolites, later stage has more qt and is infilling fractures orthogonal to primary biorturbation fabric. » « @ 138.60 S0 defined by silicious and cherty laminae. S0 tca 20° » « 140.20- 144.30 Flt »« Flt gg 60%»« Flt bx 30%»« Brco 10%» « 144.30- 149.50 Abundant qt-albite veins with minor calcite throughout interval. Flt »« Flt gg 10%»« Flt bx 50%»« Brco 40%» « 149.50- 164.20 Typical flaggy with some interbedded massive limestone sections 20-40cm thick. Limestone is more resistant to faulting and fracturing. Flt »« Flt gg 5%»« Flt bx 30%»« Brco 65%»											
164.20	317.30	USMS	632901	315.50	316.80	1.30					
USMS – Upper Siliceous Mudstone			632902	316.80	317.30	0.50					
Consists of interlaminated dark grey to black mudstone and light to medium grey chert. Regionally, a 1m thick graptolite zone occurs 15m below the top of the upper unit, this is usable as a horizon. The USMS is divided into 3 units. The Lower Unit contains abundant limestone concretions and Galena and sphalerite											

Selwyn Project Diamond Drill Log

Hole Number:
XYC-215

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		micro-concretions occur locally near the base of this unit. « gra , lm chrt -20.00% », « cg xtl sph crns ca 5.00-20.00cm », « bed chrt 10.00-15.00% » « 164.20- 177.80 Abundant pseudotachylite developed, with slick-n-lines in typical USMS with wiggly chert, calcic laminae, calcite + quartz veining is pervasive throughout. Flt »« Flt gg 20%»« Flt bx 50%»« Brco 65%» « 177.30- 184.10 Relatively competent interval of typical USMS, dark grey to black carbonaceous mudstone with calcic and cherty bands 3-7mm thick. Pyrite nodules (1-7mm) are pervasive throughout and often associated with cal-qt veins. » « 184.10- 185.90 Flt »« Flt gg 10%»« Flt bx 60%»« Brco 30%» « 185.90- 189.00 Interval of competent USMS with brecciated angular limestone clasts and abundant calcite veinlet swarms. » « 189.00- 189.70 Flt »« Flt gg 5%»« Flt bx 95%» « 189.70- 197.60 Zone of competent USMS with abundant angular and sub-rounded limestone clasts, reminerIALIZED calcite stylolites, tension gash swarms and pyrite-rich sections 2-7cm thick. » « 197.60- 211.90 In rock type described in previous interval. Flt »« Flt gg 15%»« Flt bx 60%»« Brco 25%» « 211.90- 213.60 Interval of more competent USMS, still with angular limestone clastsas described. » « 213.60- 241.00 Fault zone is large. As described in other faulted intervals of USMS in this hole. Flt »« Flt gg 25%»« Flt bx 50%»« Brco 25%» « @ 242.60 S0 defined by parallel chert banding. S0 tca 38° » « 243.70- 256.20 Major carbonaceous fault. Flt « Flt gg 20%»« Flt bx									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-215

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		60%»« Brco 20%»»									
		« 256.20- 260.40 Heavily broken zone. »									
		« 260.40- 264.50 Flt »« Flt gg 10%»« Flt bx 90%»									
		« @ 267.10 S0 defined by chert bands, planar, parallel. S0 tca 35° »									
		« 268.90- 269.30 Flt »« Flt gg 10%»« Flt bx 90%»									
		« @ 271.70 S0 defined by planar, parallel chert bands. S0 tca 35° »									
		« 274.20- 282.40 Flt »« Flt gg 10%»« Flt bx 50%»« Brco 40%»									
		« 286.10- 286.40 Finely laminated calcareous mudstone; ACTM-like appearance; trace mineralization. »									
		« 287.40- 288.20 Flt »« Flt gg 20%»« Flt bx 70%»« Brco 10%»									
		« 293.20- 296.70 Flt »« Flt gg 20%»« Flt bx 80%»									
		« @ 297.00 S0 defined by planar, parallel chert/carbonate bands. S0 tca 12° »									
		« @ 304.80 S0 defined by planar, parallel chert/carbonate bands. S0 tca 20° »									
		« @ 311.10 S0 defined by planar, parallel chert/carbonate bands. S0 tca 28° »									
		« 313.40- 314.10 Flt »« Flt gg 20%»« Flt bx 70%»									
		« 314.60- 316.70 Flt »« Flt gg 5%»« Flt bx 50%»« Brco 45%»									
317.30	340.50	ACTM	632903	317.30	318.30	1.00					
ACTM – Active Member			632904	318.30	318.70	0.40					
			632905	318.70	319.10	0.40					
			632906	319.10	319.70	0.60					
			632907	319.70	320.30	0.60					
			632908	320.30	321.50	1.20					
The ACTM consists of a repetitive, possibly rhythmic, sequence of intercalated carbonaceous mudstone, cherty mudstone, chert and limestone and locally contains economically significant Zn and Pb sulphides (see bold marked facies),											

Selwyn Project Diamond Drill Log

Hole Number:
XYC-215

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		mainly in its sections with well developed lamination. Because of its heterogeneity, the member is distinctive and easily identified.	632909	321.50	322.20	0.70					
			632910	322.20	323.30	1.10					
			632911	322.20	323.30	1.10					
		=====	632912	323.30	323.80	0.50					
		The ACTM has 8 different facies:	632913	323.80	324.50	0.70					
		=====	632914	324.50	325.10	0.60					
			632915	325.10	325.90	0.80					
		- GREY CHERT FACIES: Consists of laminated medium light grey to medium dark grey chert. Mineralization: 95-99% quartz and up to 5% secondary calcite.	632916	325.90	326.50	0.60					
			632917	326.50	327.80	1.30					
		- WHITISH GREY ZN-PB MUDSTONE FACIES: Is a laminated cherty rock containing up	632918	327.80	328.40	0.60					
		to 70% sulphides. Mineralization: quartz, sphalerite and galena are the major minerals with only minor amounts of pyrite and locally calcite. Sedimentary diagenetic structures are common and well displayed in the facies, such as:	632919	328.40	328.70	0.30					
		lamination, pseudo-beds, calcite nodules & limestone nodules and abundant water escape structures. Most obvious structure in facies is cross-cutting veins containing massive sphalerite and galena with minor pyrite. They range in width from 0.5 to 10mm.									
			632920	328.70	328.70	0.00					
			632921	328.70	329.20	0.50					
			632922	329.20	329.90	0.70					
			632923	329.90	330.70	0.80					
			632924	330.70	331.30	0.60					
			632925	331.30	332.50	1.20					
			632926	332.50	333.30	0.80					
			632927	333.30	334.30	1.00					
		- THIN BEDDED CHERTY MUDSTONE FACIES: Consists of rhythmic intercalated laminae of chert, carbonaceous mudstone and minor micrite. This facies contains significant amounts of Zn and Pb sulphides.	632928	334.30	335.00	0.70					
			632929	335.00	335.50	0.50					
			632930	335.50	335.50	0.00					
			632931	335.50	336.10	0.60					
		- CHERTY MUDSTONE FACIES: Consists of a greyish black monotonous siliceous, carbonaceous mudstone. It is most typically found overlying the thin bedded calcareous mudstone facies.	632932	336.10	336.80	0.70					
			632933	336.80	337.90	1.10					
			632934	337.90	338.50	0.60					
			632935	338.50	338.90	0.40					
		- THIN BEDDED CALCAREOUS MUDSTONE FACIES: Consists of laminated carbonaceous	632936	338.90	339.60	0.70					
		mudstone containing 20-40% calcite, 40-55% quartz and 10-20% muscovite. Sulphides occur in laminae. In the XY area it is usually the lowest facies in the section to contain laminated sulphides.									
			632937	339.60	339.90	0.30					
			632938	339.90	340.50	0.60					
		- CALCAREOUS MUDSTONE FACIES: Consists of grey to greyish black monotonous,									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-215

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		calcareous siliceous carbonaceous mudstone. There are no feathery calcite beds or pyrite-calcite blebs in the facies, making it easily distinguishable from the CCMS. - GRADED LIMESTONE FACIES: Is a laminated argillaceous limestone with intercalated carbonaceous limestone laminae. The main rock type in the facies is laminated limestone with laminae up to 0.1-7mm thick. - LIGHT GREY BASAL LIMESTONE FACIES - LGLS: Consists of laminated argillaceous limestone. In the Anniv area it marks the end of the ACTM. It's not always present in the stratigraphy. - BASAL FACIES: This is a highly contorted and locally foliated carbonaceous mudstone. Unlike the other facies it is not repeated higher in the member. It appears locally to contain the slip zone of a major slump. The facies has only been observed in the YX area. It is 0.1-2m thick. The facies consists of massive carbonaceous siliceous mudstone with lenses and laminae of contorted, slightly carbonaceous chert. « 317.30- 340.40 Very broken-up, faulted intersection; primarily low-grade mineralization with some medium-grade. » « 317.30- 318.70 Weakly brecciated silicious mudstone, very broken-up, low-grade mineralization. » « 318.70- 319.10 Brecciated texture, with a mixture of limestone, dark-grey laminated calcareous mudstone, and light grey laminated silicious mudstone in a structurally complex matrix. Visible galena stringers. Moderate mineralization.» « 319.10- 319.70 Laminated light grey limestone with weakly laminated calcareous mudstone. Low-grade mineralization. » « 319.70- 320.30 Laminated calcareous mudstone. Laminations primarily									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-215

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		defined by calcite crystals, but also by low grade mineralization. »									
		« 320.30- 321.50 Weakly laminated highly fractured, dark-grey, silicious mudstone with no visible mineralization. »									
		« 321.50- 322.20 Dark-grey silicious mudstone with abundant contorted laminations defined by moderate mineralization throughout. Includes minor visible galena nodules and minor light-grey limestone »									
		« 322.20- 323.30 Weakly laminated light-grey LMST. No visible mineralization. »									
		« 323.30- 324.50 Heavily fractured silicious med-grey mudstone. Laminated throughout, with minor limestone. Low-medium grade mineralization. »									
		« 324.50- 325.90 Weakly laminated light grey limestone. No visible mineralization. »									
		« 325.90- 327.80 Fragments are a mixture of laminated calcareous mudstone and limestone. Low-moderate mineralization. Flt »« Flt bx 10%»« Brco 80%»									
		« 327.80- 328.40 Light grey limestone. No visible mineralization. »									
		« 328.40- 328.70 Dark grey laminated silicious mudstone. Low grade mineralization. Flt »« Flt bx 90%»									
		« 328.70- 328.20 Weakly laminated, silicious mudstone. Low grade mineralization. »									
		« 329.20- 329.90 Brecciated; limestone clasts with weakly laminated silicious mudstone. Low-grade mineralization. »									
		« 329.90- 331.30 Unlaminated dark-grey silicious mudstone fragments with minor light grey limestone. No visible mineralization. Flt »« Flt gg 10%»« Flt bx 80%»									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-215

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		« 331.30- 335.00 Medium-grey, weakly laminated, weakly calcareous mudstone with minor limestone. Low grade mineralization. Very broken-up throughout. » « 335.00- 336.10 Medium-grey, silicious mudstone with no visible mineralization. Very broken-up throughout. » « 336.10- 337.90 Limestone, brecciated and heavily veined with minor calcareous mudstone. No visible mineralization. » « 337.90- 338.90 Brecciated calcareous mudstone with minor limestone. No visible mineralization. » « 338.50- 338.90 Brecciated dark-grey silicious mudstone. No visible mineralization. » « 338.90- 339.90 Unlaminated calcareous mudstone fragments. Flt »« Flt bx 80%» « 339.90- 340.50 Brecciated light grey basal limestone. »									
340.50	345.50	CCMS	632939	340.50	342.10	1.60					
		CCMS – Calcareous Mudstone Massive, calcareous, carbonaceous, dark grey mudstone. Most of the member is massive, but rare poorly defined bedding and pyrite-calcite micro-concretions are present. Most diagnostic structures are feathery calcite beds (=thin calcite-cemented concretions, many of them contain pyrite cores) and calcite pseudo-beds (= fibrous calcite vein parallel to bedding). « lm ca 5.00-10.00mm », « nodules py -3.00% 2.00-20.00mm » « 340.50- 345.50 Very broken up, but otherwise typical CCMS.» « 341.10- 341.70 Flt »« Flt bx 100%»									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-215

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
345.50	357.60	FLT									
« 345.50- 357.60 This fault zone causes displacement which results in the hole subsequently passing through USMS below. Several small faults within this fault package. Flt »« Flt gg 5%»« Flt bx 70%»« Brco 25%»			632940	342.10	371.00	28.90					
357.60	371.00	USMS									
USMS – Upper Siliceous Mudstone Consists of interlaminated dark grey to black mudstone and light to medium grey chert. Regionally, a 1m thick graptolite zone occurs 15m below the top of the upper unit, this is usable as a horizon. The USMS is divided into 3 units. The Lower Unit contains abundant limestone concretions and Galena and sphalerite micro-concretions occur locally near the base of this unit. « gra , lm chrt -20.00% », « cg xtl sph crns ca 5.00-20.00cm », « bed chrt 10.00-15.00% » « 357.60- 371.00 Competent, generally typical with abundant chert/carbonate bands and concretions. Exhibits laminations more commonly than usual and "pitted" texture common. » < @ 365.30 S0 defined by planar, parallel chert bands. S0 tca 66° >											
371.00	390.90	ACTM	632941	371.00	371.00	0.00					
ACTM – Active Member The ACTM consists of a repetitive, possibly rhythmic, sequence of intercalated carbonaceous mudstone, cherty mudstone, chert and limestone and locally contains economically significant Zn and Pb sulphides (see bold marked facies), mainly in its sections with well developed lamination. Because of its heterogeneity, the member is distinctive and easily identified. ===== The ACTM has 8 different facies:			632942	371.00	371.50	0.50					
			632943	371.50	372.10	0.60					
			632944	372.10	373.50	1.40					
			632945	373.50	374.10	0.60					
			632946	374.10	374.80	0.70					
			632947	374.80	375.70	0.90					
			632948	375.70	376.20	0.50					
			632949	376.20	376.70	0.50					
			632950	376.70	376.70	0.00					
			632951	376.70	377.40	0.70					

Selwyn Project Diamond Drill Log

Hole Number:
XYC-215

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
=====			632952	377.40	378.50	1.10					
			632953	378.50	379.00	0.50					
		- GREY CHERT FACIES: Consists of laminated medium light grey to medium dark grey chert. Mineralization: 95-99% quartz and up to 5% secondary calcite.	632954	379.00	379.60	0.60					
			632955	379.60	380.10	0.50					
			632956	380.10	380.70	0.60					
		- WHITISH GREY ZN-PB MUDSTONE FACIES: Is a laminated cherty rock containing up	632957	380.70	381.20	0.50					
		to 70% sulphides. Mineralization: quartz, sphalerite and galena are the major									
		minerals with only minor amounts of pyrite and locally calcite. Sedimentary	632958	381.20	381.80	0.60					
		diagenetic structures are common and well displayed in the facies, such as:	632959	381.80	382.50	0.70					
		lamination, pseudo-beds, calcite nodules & limestone nodules and abundant water	632960	382.50	382.50	0.00					
		escape structures. Most obvious structure in facies is cross-cutting veins	632961	382.50	383.90	1.40					
		containing massive sphalerite and galena with minor pyrite. They range in width	632962	383.90	384.70	0.80					
		from 0.5 to 10mm.	632963	384.70	385.60	0.90					
			632964	385.60	385.90	0.30					
			632965	385.90	386.20	0.30					
		- THIN BEDDED CHERTY MUDSTONE FACIES: Consists of rhythmic intercalated	632966	386.20	387.30	1.10					
		laminae of chert, carbonaceous mudstone and minor micrite. This facies contains	632967	387.30	388.20	0.90					
		significant amounts of Zn and Pb sulphides.	632968	388.20	388.90	0.70					
			632969	388.90	389.80	0.90					
		- CHERTY MUDSTONE FACIES: Consists of a greyish black monotonous siliceous,	632970	389.80	390.90	1.10					
		carbonaceous mudstone. It is most typically found overlying the thin bedded	632971	389.80	390.90	1.10					
		calcareous mudstone facies.									
		- THIN BEDDED CALCAREOUS MUDSTONE FACIES: Consists of laminated									
		carbonaceous									
		mudstone containing 20-40% calcite, 40-55% quartz and 10-20% muscovite.									
		Sulphides occur in laminae. In the XY area it is usually the lowest facies in									
		the section to contain laminated sulphides.									
		- CALCAREOUS MUDSTONE FACIES: Consists of grey to greyish black monotonous,									
		calcareous siliceous carbonaceous mudstone. There are no feathery calcite beds									
		or pyrite-calcite blebs in the facies, making it easily distinguishable from									
		the CCMS.									
		- GRADED LIMESTONE FACIES: Is a laminated argillaceous limestone with									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-215

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		intercalated carbonaceous limestone laminae. The main rock type in the facies is laminated limestone with laminae up to 0.1-7mm thick. - LIGHT GREY BASAL LIMESTONE FACIES - LGLS: Consists of laminated argillaceous limestone. In the Anniv area it marks the end of the ACTM. It's not always present in the stratigraphy. - BASAL FACIES: This is a highly contorted and locally foliated carbonaceous mudstone. Unlike the other facies it is not repeated higher in the member. It appears locally to contain the slip zone of a major slump. The facies has only been observed in the YX area. It is 0.1-2m thick. The facies consists of massive carbonaceous siliceous mudstone with lenses and laminae of contorted, slightly carbonaceous chert. « 371.00- 390.90 Second intersection, considerably more competent than the intersection above, and higher grade overall, with one moderate to high-grade intersection. » « 371.00- 371.50 Silicious laminated mudstone, very broken up, moderate to strong mineralization. » « 371.50- 372.10 Laminated limestone with minor calcareous mudstone, low-grade mineralization. » « 372.10- 373.50 Non-to-weakly calcareous mudstone with minor limestone; low grade mineralization. » « 373.50- 374.10 Classic strongly laminated medium-grade ACTM. Laminations throughout contorted and offset by micro-faults/ de-watering structures. Visible galena nodules throughout. Calcareous mudstone. » « 374.10- 375.70 Light-grey limestone with minor calcareous mudstone, unlaminated, weak mineralization. »									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-215

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		« 375.70- 376.20 Calcite/ quartz vein. »									
		« 376.20- 377.40 Light-grey limestone, unlaminated, no visible mineralization. »									
		« 377.40- 379.00 Weakly calcareous laminated mudstone. Low deformation. Low to medium mineralization. »									
		« 379.00- 379.60 Laminated light-grey limestone. No visible mineralization. »									
		« 379.60- 380.70 Laminated calcareous mudstone with minor limestone. Low deformation, low-medium mineralization. »									
		« 380.70- 381.20 Laminated limestone, low-grade mineralization. »									
		« 381.20- 382.50 Laminated calcareous mudstone, with minor limestone. Low deformation, low-medium mineralization. »									
		« 382.50- 384.70 Light-medium grey limestone with minor unlaminated calcareous mudstone. Brecciated appearance. Low-grade mineralization. »									
		« 384.70- 385.50 Weakly laminated calcareous mudstone. Weak mineralization. »									
		« 385.50- 385.90 Laminated, light grey silicious mudstone, no mineralization. »									
		« 385.90- 386.20 Fractured limestone, no mineralization. »									
		« 386.20- 387.30 Weakly laminated silicious mudstone. No mineralization visible. »									
		« 387.30- 388.90 Weakly laminated med-light grey limestone. »									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-215

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		« 388.90- 389.80 Unlaminated silicious mudstone. »									
		« 381.80- 390.90 Light grey, basal limestone. Brecciated/sheared texture. »									
390.90	432.20	CCMS									
CCMS – Calcareous Mudstone											
Massive, calcareous, carbonaceous, dark grey mudstone. Most of the member is massive, but rare poorly defined bedding and pyrite-calcite micro-concretions are present. Most diagnostic structures are feathery calcite beds (=thin calcite-cemented concretions, many of them contain pyrite cores) and calcite pseudo-beds (= fibrous calcite vein parallel to bedding).											
« lm ca 5.00-10.00mm », « nodules py -3.00% 2.00-20.00mm »											
« 390.90- 432.20 Typical, classic CCMS. »											
‹ @ 394.20 S0 defined by pyrite rich bed. S0 tca 41° ›											
‹ @ 410.10 S0 defined by pyrite rich bed. S0 tca 48° ›											
‹ @ 418.90 S0 defined by pyrite rich bed. S0 tca 39° ›											
‹ @ 421.00 S0 defined by pyrite rich bed. S0 tca 32° ›											
‹ @ 430.50 S0 defined by pyrite rich bed. S0 tca 38° ›											
432.20	432.20	EOH									

Diamond Drill Log

Comprehensive Report for Hole:

XYC-214

Hole No.: XYC-214	Depth: 248.50 m	Horizontal Length: 0.00 m	Project: 1710
Location Data:			
Property:	Selwyn Project	Claim Name:	X 46
Mining District:	Selwyn Basin	Grant Number:	Y 64679
Province/Territory:	Yukon		
UTM Co-Ordinates & Altitude of Drill Hole Collar:			
UTM Easting:	487284.00 m	True Azimuth:	40.0 °
UTM Northing:	6927260.00 m	Hole Angle:	-69.0 °
Elevation (m):	1417.00 m	NTS Name:	Placer Creek
		NTS Number:	105I06
Grid Co-Ordinates of Drill Hole Collar:			
Grid Easting (m):	0.00 m	Grid Name:	HP 06
Grid Northing (m):	0.00 m	Grid Type:	100m
Grid Azimuth:	100.0 °		
Dimond Drilling Contract:			
Drilled By:	NL-03	Date Drilling Start:	09/22/2010
		Date Finish:	09/26/2010
Diamond Drill Core:			
Logged By:	Kate Cameron / Matt Jodrey	Date Logging Start:	09/26/2010
		Date Finish:	09/26/2010
Legend for Core Logging Codes: PAX			
Core Size:	NQ	Cemented:	Yes
Casing Depth:	6.40 m	Casing Pulled:	Yes
Water Depth:	0.00 m	Overburden Depth:	6.40 m
Level:			
Section:		Drift:	

Selwyn Project

Diamond Drill Log

Survey Data for Hole

XYC-214

Hole Comments:

Thu, Sep 23 --- New hole started at new setup in XY West. 20 feet of casing in, and core to 31 ft. No issues to report.

=====

Fri, Sep 24 --- Currently in Flaggy at 76 m. Some waterline problems, and small drill pad.

=====

Sat, Sep 25 --- Huge dayshift yesterday. Current depth 228 m in heavily fractured USMS.

=====

Sun, Sep 26 --- Currently in very bad ground within USMS at a depth of 247 m. Rod has been stuck for 24 hrs, they are still trying to get it unstuck today. Awaiting further direction.

<i>Depth</i>	<i>Dip</i>	<i>Azimuth</i>
0.00	-69.0	40.0
48.20	-69.1	41.2
93.90	-69.5	34.1
139.60	-69.4	35.8
182.90	-69.7	34.0
231.00	-69.2	35.6

Selwyn Project Diamond Drill Log

Hole Number:
XYC-214

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
0.00	6.40	OVBR									
6.40	49.10	BSSM	635001	28.70	29.70	1.00					
BSSM – Backside Siliceous Mudstone			635002	29.70	30.20	0.50					
Devonian Siliceous Mudstone – Upper Chert Formation			635003	30.20	30.50	0.30					
Greyish black laminated chert and siliceous mudstone. Randomly-oriented to bedding-parallel bioturbation is common in the bottom of the unit. « lm chrt 75.00-95.00% », « btrb 0.10-2.00cm »,			635004	30.50	31.00	0.50					
« 6.40- 9.50 Laminated lmst, lt grey »			635005	30.50	31.00	0.50					
« 9.50- 33.40 FLT »			635006	30.50	30.50	0.00					
« 9.50- 33.40 brkn core 40%»« flt bx 60%»« flt gg 20%»			635007	30.50	30.50	0.00					
« 9.50- 15.20 Very broken up laminated mdst in FLT »											
« 15.20- 28.30 Lmst with intense ca veining. Abundant py associated with ca. In flt, some mdst rich sections »											
« 28.30- 49.10 Dark grey mdst, somewhat Si and carb with v. frequent ca stringers in spidery pattern. Ca veins py bx. Py conc. with ca halo »											
« 28.30- 32.20 Laminated, rich in v. fine py (on lams). Lams are wavy and sub-parallel TCA, irregular. Very high in py. »											
< @ 30.00 5cm section of galena mx in stringers <1mm wide hosted in pyrite. >											
< @ 39.70 Fol/ca veins ~10 and 20 degrees TCA. Bedding in weak lam 20-25 degrees TCA >											
49.10	168.00	FLMD									
FLMD – Flaggy Mudstone Formation											
Dark grey mudstone in the upper portions of the unit grading into light grey											

Selwyn Project Diamond Drill Log

Hole Number:
XYC-214

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		mudstone to siltstone. Contains abundant wispy bioturbation which ranges from randomly-oriented at the top of the unit to bedding-parallel throughout the majority of the unit. Darker upper section has a strong fetid odour along broken surfaces. « btrb 0.10-2.00cm », « cg xtl crns ca 1.00-5.00% 5.00-150.00cm », « crns py 1.00-5.00% 0.10-0.50mm » , Typical Flaggy Mudstone. Beds are bioturbated or intensely microfaulted syn-depositionally. Concretions of pyrite associated with calcite are common. Varys from dark grey. Abundant calcite as "spidery" stringers and veins. < @ 49.90 Original bedding of darker layers S0 tca 45° > < @ 49.10 Foliation and distortion of beds S1 30° > < @ 61.40 Foliation and distortion of beds, original bedding impossible to determine S1 tca 15° > < @ 70.10 Foliation and distortion S1 tca 10° > < @ 75.30 Planar carbonaceous beds S0 tca 46° > < @ 92.00 Planar carbonaceous beds S0 tca 46° > « 103.00- 108.60 FLT »« flt bx 40%»« flt gg 10%»« brkn core 50%» < @ 122.30 Carbonaceous beds S0 tca 50° > < @ 141.80 Carbonaceous bed S0 tca 50° > « 149.40- 168.00 BRKN ZONE »									
168.00	218.30	USMS									
		USMS – Upper Siliceous Mudstone Consists of interlaminated dark grey to black mudstone and light to medium grey chert. Regionally, a 1m thick graptolite zone occurs 15m below the top of the upper unit, this is usable as a horizon. The USMS is divided into 3 units. The Lower Unit contains abundant limestone concretions and Galena and sphalerite micro-concretions occur locally near the base of this unit. « gra , lm chrt -20.00% », « cg xtl sph crns ca 5.00-20.00cm », « bed chrt 10.00-15.00% », Very broken up/ faulted throughout. Lithologically typical, abundant chert/									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-214

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		carbonate banding. « 168.00- 169.60 FLT »« flt bx 60%»« flt gg 10%»« brkn core 30%» < @ 174.40 Calcite-rich fine laminations S0 tca 50° > « 178.30- 202.70 Highly broken zone, combines several large fault zones FLT » « 178.30- 181.80 FLT »« flt bx 50%»« flt gg 15%»« brkn core 35%» « 182.80- 184.10 FLT »« flt bx 50%»« brkn core 50%» « 189.40- 202.20 Massive carbonaceous fault zone. FLT »« flt bx 60%»« flt gg 10%»« brkn core 30%» < @ 196.20 Planar parallel chert bands S0 tca 36° > < @ 209.90 Parallel chert/carbonate bands. Varies locally S0 tca 58° >									
		218.30 221.90 FLT ----- Fault does not appear to be overly significant, without an abundance of fault breccia or fault gouge. However, immediately after the fault a short section of Flaggy Mudstone occurs, indicating significant displacement here. Fracture surfaces show well developed slicken-surfaces throughout. Flt bx: 20% Flt gg: 5% Brkn: 75%									
		221.90 227.40 FLMD ----- FLMD – Flaggy Mudstone Formation Dark grey mudstone in the upper portions of the unit grading into light grey mudstone to siltstone. Contains abundant wispy bioturbation which ranges from randomly-oriented at the top of the unit to bedding-parallel throughout the majority of the unit. Darker upper section has a strong fetid odour along broken surfaces. « btrb 0.10-2.00cm », « cg xtl crns ca 1.00-5.00%									

Diamond Drill Log

Comprehensive Report for Hole:

XYC-213

Hole No.: XYC-213	Depth: 273.70 m	Horizontal Length: 0.00 m	Project: 1710
Location Data:			
Property:	Selwyn Project	Claim Name:	X 11
Mining District:	Selwyn Basin	Grant Number:	Y 64527
Province/Territory:	Yukon		
UTM Co-Ordinates & Altitude of Drill Hole Collar:			
UTM Easting:	488350.00 m	True Azimuth:	30.0 °
UTM Northing:	6926635.00 m	Hole Angle:	-87.0 °
Elevation (m):	1562.00 m	NTS Name:	Placer Creek
		NTS Number:	105L06
Grid Co-Ordinates of Drill Hole Collar:			
Grid Easting (m):	0.00 m	Grid Name:	HP 06
Grid Northing (m):	0.00 m	Grid Type:	100m
Grid Azimuth:	90.0 °		
Dimond Drilling Contract:			
Drilled By:	NL-02	Date Drilling Start:	09/23/2010
		Date Finish:	09/26/2010
Diamond Drill Core:			
Logged By:	Graham Leroux / Kate	Date Logging Start:	09/27/2010
		Date Finish:	10/24/2010
Legend for Core Logging Codes: PAX			
Core Size:	NQ3	Cemented:	Yes
Casing Depth:	10.70 m	Casing Pulled:	Yes
Water Depth:	0.00 m	Overburden Depth:	10.70 m
Level:	Section:	Drift:	

Selwyn Project

Diamond Drill Log

Survey Data for Hole

XYC-213

Hole Comments:

Thu, Sep 23 --- Casing at new site, #26. Quick and easy drill move.

=====

Fri, Sep 24 --- Huge shift yesterday. Currently at 135 m in USMS. Contact between Flaggy and USMS is at approx. 120 m.

=====

Sat, Sep 25 --- Current depth 180 m in USMS. There appears to be a Flexit test error or the hole is deviating more than seems possible.

=====

Sun, Sep 26 --- Intercepted ACTM from approx. 211 m to 227 m. Currently in CCMS at 273 m. Hole shutting down. Moving to setup #30.

<i>Depth</i>	<i>Dip</i>	<i>Azimuth</i>
0.00	-87.0	30.0
55.00	-87.1	32.6
101.00	-88.5	62.1
150.00	-87.8	128.1
200.00	-88.5	127.7
250.00	-87.7	127.4
273.50	-86.8	138.3

Selwyn Project Diamond Drill Log

Hole Number:
XYC-213

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
0.00	10.70	OVBR									
10.70	20.50	BSSM									
<i>BSSM – Backside Siliceous Mudstone</i>											
<i>Devonian Siliceous Mudstone – Upper Chert Formation</i>											
<i>Greyish black laminated chert and siliceous mudstone. Randomly-oriented to bedding-parallel bioturbation is common in the bottom of the unit. « lm chrt 75.00-95.00% », « btrb 0.10-2.00cm »,</i>											
<i>« 10.70- 14.90 friable, siliceous cherty mudstone, greyish black with laminae defined by grey cherty layers. Pyritic laminae do occur but they are minor, trace disseminated fine grained pyrite is pervasive. There are abundant qt-cal veining that has two stages. early stage is defined mostly by tension gashes and the later stage is defined by random and spider-style qt +/- cal veins with offshoots forming stylolites.»</i>											
<i>< @ 17.50 defined by laminae S0 35° tca ></i>											
<i>« 14.90- 20.50 Rock type becomes cohesive as veining starts to localize. Some veins have internal pyrite that appears to be over-printed by tension gashes. »</i>											
20.50	127.60	FLMD									
<i>FLMD – Flaggy Mudstone Formation</i>											
<i>Dark grey mudstone in the upper portions of the unit grading into light grey mudstone to siltstone. Contains abundant wispy bioturbation which ranges from randomly-oriented at the top of the unit to bedding-parallel throughout the majority of the unit. Darker upper section has a strong fetid odour along broken surfaces. « btrb 0.10-2.00cm », « cg xtl crns ca 1.00-5.00% 5.00-150.00cm », « crns py 1.00-5.00% 0.10-0.50mm »</i>											
<i>« 20.50- 41.55 Heavily bioturbated, structures are parallel to S0 ~25</i>											

Selwyn Project Diamond Drill Log

Hole Number:
XYC-213

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		degrees tca. Pyrite concretions up to 3-6cm often have rims of qt-calcite. Jagged cusped stylolites sometimes mark depositional boundaries between beds. Spots of pyrite are pervasive and are typically on a mm-scale. » « 41.55- 43.20 mostly fault gouge, but drillers did a great job removing gouge from tubes intact. Mostly incohesive devitrified fault gouge and breccia. FLT »« Flt gg 50%»« Flt bx 25%»« Brco 25%» « 43.20- 46.95 Heavily fractured and veined with calcite +/- quartz, bioturbation features are more random in this section. Blocky pyrite concretions (mm-scale) are still pervasive. Mostly this section is massive and cherty. » « 46.95- 49.90 Light grey, cherty where whole core exists, abundant mosaic fractures help to brecciate rock. Gouge zones appear partially devitrified. FLT »« Flt gg 10%»« Flt bx 80%»« Brco 80%» « 49.90- 52.60 Lower zone fault breccia, only minor gouge and abundant fracturing infilling with calcite +/- quartz. » « 52.60- 64.20 Light grey bioturbated mudstone with abundant and pervasive pyrite concretions (mm-scale). Bioturbation structures have a regular orientation that is conformable to S0: ~25 degrees tca. Early stage calcite veining also follows this trend. Some pyrite-rich zones display splotches and blebs of pyrite with no internal geometry. Late stage calcite-quartz veins appear like tension gashes orthogonal to bioturbation structures. Lower in this interval quartz veins dominate over calcite veins and pyrite content is rare, often associated with quartz. The majority of tension gashes appear as later-stage than cm-scale quartz veining. » « 64.20- 64.30 Devitrified fault gouge and breccia. FLT »« Flt gg 50%»« Flt bx 50%» « 64.30- 67.00 Heavily bioturbated light to medium grey mudstone with micro en echelon veining that is overprinted by larger quartz veins. En echelon									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-213

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		structure suggests sinistral-sense extension. Pyrite concretions up to 2cm commonly with rims of calcite and quartz, also splotches of pyrite up to 5cm. Bioturbation structures typically are conformable to S0, however they may be convoluted in some cases. » « 67.00- 77.20 Splay faulting- this is a zone of heavily faulted rock, mostly breccia and gouge but there are zones of cohesive rock. Abundant pseudotachylite in some areas, often displaying slick-n-lines. Pyrite is localized in zones of intense quartz veining. FLT »« Flt gg 45%»« Flt bx 30%»« Brco 25%» « 77.20- 79.10 Abundant pseudotachylite and quartz veining with minor calcite. Lots of wispy bioturbation structures in grey mudstone beneath black pseudotachylite. » « 79.10- 107.50 Medium to light grey, heavily bioturbated mudstone all with conformable attitude. S0 ~30 degrees tca to central axis. Cm-wide quartz tension gashes indicate sinistral-sense shearing. At ~90.6m there appears to be some limestone filled burrows +/- quartz. Pyrite concretions are ~1% to <1%, pervasive and often rimmed with quartz +/- calcite. Pyrite-rich layers up to 6cm thick to occur but mostly pyrite is concretionary. » « 107.50- 122.20 Bioturbated mudstone, pyrite concretions with quartz-calcite rims. » < @ 107.90 S0 tca 38° > « 108.30- 110.50 Heavily fractured area with minor gouge and recrystallized quartz. » « 110.50- 114.30 Bioturbation is conformable to S0. Pyrite concretions up to 3-4cm +/- rims of quartz+calcite. Concentrated zones of irregular and oblique stylolites. » < @ 112.70 S0 tca 28° >									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-213

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		« 114.30- 116.20 Fault zone. Carbonaceous in fault with recrystallized quartz. FLT »« Flt gg 10%»« Flt bx 80%»« Brco 10%» < @ 116.30 S0 tca 25° > « 116.20- 118.40 Easily fractured mudstone. Lots of tension gashes, and recrystallized quartz. Stretched out limestone fragments near base of interval. » « 118.40- 118.70 Highly calcareous zone with sharp contacts. Splayed tension gashes. » « 118.70- 122.20 Dark grey slightly bioturbated mudstone with abundant pyrite concretions on cm-scale, the larger they are the more heavily rimmed they get. » < @ 121.80 S0 tca 38° > < @ 124.20 S0 defined by slightly distorted (bioturbated) muddy layers in lighter matrix. S0 tca 25° >									
127.60	204.50	USMS	633439	151.00	152.00	1.00	0.01	0.01	1.00	5.00	2.00
		USMS – Upper Siliceous Mudstone	633440	152.00	153.00	1.00	0.01	0.20	1.00	5.00	0.05
			633441	153.00	153.40	0.40	0.01	0.45	3.00	20.00	0.02
			633442	153.40	154.40	1.00	0.01	0.10	1.00	5.00	0.10
			633401	201.70	202.70	1.00	0.02	0.34	1.00	10.00	0.06
		Consists of interlaminated dark grey to black mudstone and light to medium grey chert. Regionally, a 1m thick graptolite zone occurs 15m below the top of the upper unit, this is usable as a horizon. The USMS is divided into 3 units. The Lower Unit contains abundant limestone concretions and Galena and sphalerite micro-concretions occur locally near the base of this unit. « gra , lm chrt -20.00% », « cg xtl sph crns ca 5.00-20.00cm », « bed chrt 10.00-15.00% », -----									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-213

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		----- Classic. Pyrite blebs with calcite halos. Chert banding. Traces of mineralization indicated by the Niton (very low levels). < @ 141.60 Bedding in chert bands S0 TCA 35° > < @ 153.10 Bedding in three cm of faint sphalerite laminae S0 TCA 35° > < @ 153.40 Bedding in parallel planar calcite veins and elongate pyrite blebs. S0 TCA 40° > « 154.40- 155.20 FLT »« flt bx 50%»« flt gg 50%» « 156.70- 159.20 Fault zone. Several faults grouped together; minor slicken slides. FLT »« brco 20%»« flt bx 30%»« flt gg 10%» « 160.30- 161.20 Fault Some of the core pieces may be re-constituted gouge and breccia. FLT »« brco 70%»« flt bx 20%»« flt gg 10%» < @ 166.50 Bedding in faint lamination and chert bands. S0 TCA 40° > « 167.40- 167.50 FLT »« flt bx 10%»« flt gg 90%» < @ 171.00 Bedding in faint lamination S0 TCA 20° > « 172.60- 172.90 FLT »« brco 40%»« flt bx 50%»« flt gg 10%» « 178.30- 190.50 Fault zone. Set of closely spaced faults, core lost. FLT »« brco 10%»« flt bx 20%»« flt gg 30%» < @ 191.70 Bedding in chert bands and faint lamination S0 TCA 25° > « 192.30- 197.20 FLT »« brco 10%»« flt bx 30%»« flt gg 10%»									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-213

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
			633402	202.70	204.60	1.90	0.71	0.72	1.00	30.00	0.99
204.50	231.90	ACTM	633403	204.60	206.50	1.90	0.94	1.40	1.00	70.00	0.67
<i>ACTM – Active Member</i>			633404	206.50	206.80	0.30	6.88	16.49	5.00	760.00	0.42
<i>The ACTM consists of a repetitive, possibly rhythmic, sequence of intercalated carbonaceous mudstone, cherty mudstone, chert and limestone and locally contains economically significant Zn and Pb sulphides (see bold marked facies), mainly in its sections with well developed lamination. Because of its heterogeneity, the member is distinctive and easily identified.</i> ===== <i>The ACTM has 8 different facies:</i> ===== - GREY CHERT FACIES: <i>Consists of laminated medium light grey to medium dark grey chert. Mineralization: 95-99% quartz and up to 5% secondary calcite.</i> - WHITISH GREY ZN-PB MUDSTONE FACIES: <i>Is a laminated cherty rock containing up to 70% sulphides. Mineralization: quartz, sphalerite and galena are the major minerals with only minor amounts of pyrite and locally calcite. Sedimentary diagenetic structures are common and well displayed in the facies, such as: lamination, pseudo-beds, calcite nodules & limestone nodules and abundant water escape structures. Most obvious structure in facies is cross-cutting veins containing massive sphalerite and galena with minor pyrite. They range in width from 0.5 to 10mm.</i> - THIN BEDDED CHERTY MUDSTONE FACIES: <i>Consists of rhythmic intercalated laminae of chert, carbonaceous mudstone and minor micrite. This facies contains significant amounts of Zn and Pb sulphides.</i> - CHERTY MUDSTONE FACIES: <i>Consists of a greyish black monotonous siliceous, carbonaceous mudstone. It is most typically found overlying the thin bedded calcareous mudstone facies.</i>			633405	206.80	207.80	1.00	0.57	3.52	1.00	80.00	0.16
			633406	207.80	208.80	1.00	1.24	4.84	1.00	140.00	0.26
			633407	208.80	209.10	0.30	1.23	2.28	1.00	80.00	0.54
			633408	209.10	209.60	0.50	1.37	1.68	1.00	80.00	0.82
			633409	209.60	210.40	0.80	0.08	1.19	1.00	40.00	0.07
			633410	210.40	212.20	1.80	0.13	0.60	1.00	20.00	0.22
			633411	210.40	212.20	1.80	0.12	0.45	1.00	10.00	0.27
			633412	212.20	212.70	0.50	1.82	11.11	1.00	280.00	0.16
			633413	212.70	213.00	0.30	0.99	2.34	1.00	80.00	0.42
			633414	213.00	213.70	0.70	0.36	0.18	1.00	5.00	2.00
			633415	213.70	214.80	1.10	0.85	0.75	1.00	20.00	1.13
			633416	214.80	215.10	0.30	0.06	0.87	1.00	20.00	0.07
			633417	215.10	215.60	0.50	0.35	0.34	1.00	5.00	1.03
			633418	215.60	216.40	0.80	1.87	5.88	1.00	180.00	0.32
			633419	216.40	217.50	1.10	1.47	4.59	1.00	120.00	0.32
			633420	217.50	217.50	0.00	0.01	0.01	1.00	5.00	2.00
			633421	217.50	218.50	1.00	1.34	4.53	1.00	110.00	0.30
			633422	218.50	219.90	1.40	1.22	6.71	1.00	190.00	0.18
			633423	219.90	220.80	0.90	0.57	1.08	1.00	20.00	0.53
			633424	220.80	222.30	1.50	0.01	0.02	1.00	5.00	0.50
			633425	222.30	224.20	1.90	0.01	0.01	1.00	5.00	1.00
			633426	224.20	225.10	0.90	0.18	0.01	1.00	5.00	36.00
			633427	225.10	225.40	0.30	0.08	0.01	1.00	5.00	16.00
			633428	225.40	225.70	0.30	0.06	0.02	1.00	5.00	3.00
			633429	225.70	226.70	1.00	0.01	0.02	1.00	5.00	0.50
			633430	226.70	226.70	0.00	6.24	6.66	70.00	180.00	0.94
			633431	226.70	229.30	2.60	0.04	0.15	1.00	5.00	0.27
			633432	229.30	230.90	1.60	0.01	0.01	1.00	5.00	2.00

Selwyn Project Diamond Drill Log

Hole Number:
XYC-213

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		- <i>THIN BEDDED CALCAREOUS MUDSTONE FACIES: Consists of laminated carbonaceous mudstone containing 20-40% calcite, 40-55% quartz and 10-20% muscovite. Sulphides occur in laminae. In the XY area it is usually the lowest facies in the section to contain laminated sulphides.</i> - <i>CALCAREOUS MUDSTONE FACIES: Consists of grey to greyish black monotonous, calcareous siliceous carbonaceous mudstone. There are no feathery calcite beds or pyrite-calcite blebs in the facies, making it easily distinguishable from the CCMS.</i> - <i>GRADED LIMESTONE FACIES: Is a laminated argillaceous limestone with intercalated carbonaceous limestone laminae. The main rock type in the facies is laminated limestone with laminae up to 0.1-7mm thick.</i> - <i>LIGHT GREY BASAL LIMESTONE FACIES - LGLS: Consists of laminated argillaceous limestone. In the Anniv area it marks the end of the ACTM. It's not always present in the stratigraphy.</i> - <i>BASAL FACIES: This is a highly contorted and locally foliated carbonaceous mudstone. Unlike the other facies it is not repeated higher in the member. It appears locally to contain the slip zone of a major slump. The facies has only been observed in the YX area. It is 0.1-2m thick. The facies consists of massive carbonaceous siliceous mudstone with lenses and laminae of contorted, slightly carbonaceous chert.</i> ----- ----- Short intercept of active; only one small section of high grade. The rest is fairly typical.									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-213

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		« 204.50- 206.50 Medium to dark grey siliceous mudstone with abundant calcite and pyrite veining. Weak distorted lamination containing sphalerite. »									
		« 206.50- 206.80 Light brownish grey siliceous mudstone. High grade mineralization. Desnse, fine laminae of sphalerite and 2 mm veins of galena. Perhaps 15-25% combined. »									
		« 206.80- 207.80 Medium to dark grey mudstone with abundant sphalerite laminae (15% galena?). Trace galena. »									
		« 207.80- 208.80 Calcareous mudstone, light or medium grey, laminae contain sphalerite. Calcite veins with pyrite. »									
		« 208.80- 209.10 Medium grey siliceous mudstone without veins or laminae. No visible mineralization. »									
		« 209.10- 209.60 Light grey laminated mudstone with infrequent calcite veins. Might have some trace galena and sphalerite visible in laminae. »									
		« 209.60- 210.40 Black to medium grey massive mudstone. No visible mineralization. Trace mineralization found by Niton.»									
		« 210.40- 211.70 FLT »« brco 10%»« flt bx 90%»									
		« 210.40- 212.20 Black massive mudstone. No visible mineralization. Trace mineralization found by Niton.Whispy calcite veins. Siliceous. »									
		« 212.20- 212.70 Typical good grade ACTM. Mix of dark and light grey laminae that contain pyrite and sphalerite. Galena is in small belbs with calcite. Limestone concr etions or clasts are present. Section transitions from siliceous mudstone at the top to calcareous mudstone at the bottom although the mineralization is uniform throughout. »									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-213

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		« 212.70- 213.00 Coarse, laminated, light grey limestone with trace sphalerite. »									
		« 213.00- 214.80 Laminated limestone and calcareous mudstone. Light grey. Abundant calcite stringers. No visible mineralization. Trace mineralization found by Niton.»									
		« 214.80- 215.10 Medium grey calcareous mudstone. Whispy calcite stringers. No visible mineralization. Trace mineralization found by Niton. »									
		« 215.10- 215.60 Laminated limestone and calcareous mudstone. Light grey. Abundant calcite stringers. No visible mineralization. Trace mineralization found by Niton. »									
		« 215.60- 216.40 Dark grey to black mudstone. Very weakly calcareous. Some lamination containing galena and sphalerite. »									
		« 216.40- 219.90 Laminated limestone and medium grey calcareous mudstone. Sphalerite visible in laminae. »									
		« 219.90- 222.30 Laminated limestone and medium grey calcareous mudstone. Increased calcite stringers. No visible mineralization. Trace mineralization found by Niton. »									
		« 222.30- 225.40 Laminated limestone and medium grey calcareous mudstone. Visible galena in two very small veins. »									
		« 224.90- 225.10 Fault. Core lost. Only 10 cm recovered. FLT »« flt bx 90%»« flt gg 10%»									
		« 225.40- 225.70 Black mudstone. Slightly calcareous. Faint laminae with									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-213

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		sphalerite. »									
		« 225.70- 226.70 Laminated limestone and medium grey calcareous mudstone. Increased calcite stringers. No visible mineralization. Niton: trace mineralization. »									
		« 226.70- 229.30 Black carbonaceous mudstone. Few features (mostly fault gouge). »									
		« 226.90- 229.30 Fault. FLT »« flt bx 10%»« flt gg 90%»									
		« 229.30- 232.00 Basal limestone. Lery light grey. Abundant 0.5 to 1 cm calcite veins. Competent. Interbedded black mudstone starts to occur half way through and inrea ses down hole. »									
			633433	230.90	232.00	1.10	0.01	0.04	2.00	5.00	0.25
231.90	273.70	CCMS	633434	232.00	233.70	1.70	0.01	0.01	2.00	5.00	1.00
		CCMS – Calcareous Mudstone	633435	233.70	235.00	1.30	0.01	0.02	2.00	5.00	0.50
			633436	233.70	235.00	1.30	0.01	0.02	1.00	5.00	0.50
		Massive, calcareous, carbonaceous, dark grey mudstone. Most of the member is massive, but rare poorly defined bedding and pyrite-calcite micro-concretions are present. Most diagnostic structures are feathery calcite beds (=thin calcite-cemented concretions, many of them contain pyrite cores) and calcite pseudo-beds (= fibrous calcite vein parallel to bedding).	633437	235.00	235.00	0.00	0.01	0.01	1.00	5.00	2.00
			633438	235.00	235.00	0.00	1.45	3.00	20.00	180.00	0.48
		« lm ca 5.00-10.00mm », « nodules py -3.00% 2.00-20.00mm »,									
		Classic.									
		« 231.90- 234.70 Fault. Reconstituted breccia and gouge. FLT »« brco 10%»« flt bx 20%»« flt gg 70%»									
		« 235.10- 239.70 Fault and broken zone. No recovery between 235.1 and 235.8. Some mechanical breakage. Rock is very fissile. FLT »« brco 20%»« flt bx									



Selwyn Project Diamond Drill Log

Hole Number:
XYC-213

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		50%»« flt gg 10%» « 249.20- 252.30 Fault and broken zone. FLT »« brco 30%»« flt bx 50%»« flt gg 10%»									
273.70	273.70	EOH									

Diamond Drill Log

Comprehensive Report for Hole:

XYC-212

Hole No.: XYC-212	Depth: 297.10 m	Horizontal Length: 0.00 m	Project: 1710
Location Data:			
Property:	Selwyn Project	Claim Name:	X 13
Mining District:	Selwyn Basin	Grant Number:	Y 64538
Province/Territory:	Yukon		
UTM Co-Ordinates & Altitude of Drill Hole Collar:			
UTM Easting:	488980.00 m	True Azimuth:	210.0 °
UTM Northing:	6926421.00 m	Hole Angle:	-72.0 °
Elevation (m):	1654.00 m	NTS Name:	Placer Creek
		NTS Number:	105L06
Grid Co-Ordinates of Drill Hole Collar:			
Grid Easting (m):	0.00 m	Grid Name:	HP 06
Grid Northing (m):	0.00 m	Grid Type:	100m
Grid Azimuth:	270.0 °		
Dimond Drilling Contract:			
Drilled By:	NL-03	Date Drilling Start:	09/19/2010
		Date Finish:	09/22/2010
Diamond Drill Core:			
Logged By:	Graham Leroux / Kate	Date Logging Start:	09/24/2010
		Date Finish:	10/08/2010
Legend for Core Logging Codes: PAX			
Core Size:	NQ	Cemented:	Yes
Casing Depth:	9.50 m	Casing Pulled:	Yes
Water Depth:	0.00 m	Overburden Depth:	9.50 m
Level:	Section:	Drift:	

Selwyn Project

Diamond Drill Log

Survey Data for Hole

XYC-212

Hole Comments:

Mon, Sep 20 --- New hole started, current depth 39 m. No issues to report. Unit is Flaggy Mudstone.

=====

Tue, Sep 21 --- 300 ft day shift blew past the oriented core start point. There has been no intercept with ACTM. Large broken/rubble zone from ~150 m to current depth of 178 m.

=====

Wed, Sep 22 --- No significant intercept of ACTM has been found. Drilling continues in CCMS at 276 m.

<i>Depth</i>	<i>Dip</i>	<i>Azimuth</i>
0.00	-72.0	210.0
48.20	-71.6	214.8
93.90	-70.9	220.8
139.60	-70.4	217.8
185.00	-69.6	215.4
234.10	-68.7	218.4
276.80	-68.4	217.5
297.20	-68.1	220.9

Selwyn Project Diamond Drill Log

Hole Number:
XYC-212

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
0.00	9.50	OVBR									
9.50	112.10	FLMD									
FLMD – Flaggy Mudstone Formation											
Dark grey mudstone in the upper portions of the unit grading into light grey mudstone to siltstone. Contains abundant wispy bioturbation which ranges from randomly-oriented at the top of the unit to bedding-parallel throughout the majority of the unit. Darker upper section has a strong fetid odour along broken surfaces. « btrb 0.10-2.00cm », « cg xtl crns ca 1.00-5.00% 5.00-150.00cm », « crns py 1.00-5.00% 0.10-0.50mm »,											
«Transition from dark 'bioturbated' mudstone beds in light grey matrix to more mudstone dominated bioturbated sections. Sections 20cm to 1m are massive, black mudstone with traces of disseminated pyrite. Uper 50m is broken up intensely. Siliceous. Calcite-quartz veins on mm-scale cross-cut foliation + apparent bedding. 45-50 degrees tca. Calcite veins 3cm wide.»											
◁ @ 86.00 dark feathery bands S0, tca 65° ▷											
« 71.40- 74.00 massive black mudstone »											
« 78.00- 79.40 Transitional contact to mudstone, black with faint laminations. »											
◁ @ 95.00 flaggy bedding S0, tca 50° ▷											
◁ @ 71.40 flaggy bedding S0, tca 35° ▷											
« 104.80- 105.70 large calcite vein »											
112.10	212.50	USMS	633101	210.50	211.90	1.40	0.34	0.24	1.00	5.00	1.42
USMS – Upper Siliceous Mudstone			633102	211.90	212.50	0.60	0.01	0.25	1.00	5.00	0.04

Selwyn Project Diamond Drill Log

Hole Number:
XYC-212

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		Consists of interlaminated dark grey to black mudstone and light to medium grey chert. Regionally, a 1m thick graptolite zone occurs 15m below the top of the upper unit, this is usable as a horizon. The USMS is divided into 3 units. The Lower Unit contains abundant limestone concretions and Galena and sphalerite micro-concretions occur locally near the base of this unit. « gra , lm chrt -20.00% », « cg xtl sph crns ca 5.00-20.00cm », « bed chrt 10.00-15.00% », « 112.10- 127.40 Black, highly carbonaceous, weakly calcareous mudstone. Disseminated pyrite (<1%) in a specular and blebby fashion, pyrite faintly outlines laminae. Calcite veins and specs often are associated with pyrite. Abundant 2-4mm wormy chert and calcareous bands. Laminae are contorted and often irregular. Minor faulting and breccia occurs near the bottom of this range feature. » « 127.40- 128.40 FLT »« gg 15%»« bx 80%»« Brco 5%» « 128.40- 132.60 Carbonaceous musdstone, lots of broken core pieces. This interval is still minorly affected by the fault zone listed in the last range feature. There is abundant pseudotachylite and some fracture surfaces have slick-n-line on them . » « 132.60- 154.70 Black, carbonaceous mudstone with abundant kinked and contorted calcareou-rich, as well as cherty bands. Calcic veining is later stage and can be discordant to S0, also it commonly fills in along laminae. S0 ranged from a few mm to a few cm. Late stage calcic veining is often associated with pyrite that can be brecciated within the calcic matrix. Light grey oblong irregular limestone 'concretions' do occur but account for <5% of interval, typically ranging in size from mm-scale up to 35cm. Specular traces of pyrite are pervasive. Soft-sed deformation features are numerous, mostly consisting of slump, load and flame structures. S0 is largely difined by cherty and calcic and cherty bands which only have a minor amount of consistency. Irregular stylolites are remineralized by calcite and minor quartz. Many thin fractures show internal slippage of this rock has occured --> with development of slick-n-lines on psuedoachylite surfaces. »									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-212

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		◁ @ 134.70 defined by calcite laminae among other laminae S0, tca 66° ▷ ◁ @ 140.80 defined by elongate pyrite blebs and calcic laminae S0, tca 33° ▷ ◁ @ 146.60 defined by chert and calcic bands S0, tca 38° ▷ « 154.70- 155.70 FLT »« gg 15%»« bx 25%»« Brco 60%» « 155.70- 157.32 Laminated carbonaceous mudstone, as described. One zone of lighter sulphide-rich laminae that has slumped into place runs 1.7% Zn over 3cm, no where else is there this type of mineralization, it is isolated and anomalous. » « 157.30- 158.20 Faulting is parallel to core axis and results in a pencil-like fissile fracturing with abundant slick-n-lines on faulting surfaces FLT »« gg »« bx 15%»« Brco 85%» « 158.20- 159.00 Carbonaceous mudstone as described, trace-trace disseminated pyrite. » « 159.00- 160.00 Limstone 'concretion'. 5cm calcite veins runs through it. Also there are some dirty patches with convoluted carbonaceous mudstone in them. (Not really typical of a concretion-more like a clast) » « 160.00- 162.50 Carbonaeous mudstone, as described, highly contorted cherty and calcic bands. Micro-stylolites infilled by calcite also. » « 162.50- 165.70 FLT- Although this fault interval is mostly broken core, there is strong evidence of rock strain represented by S0-parallel slick-n-sides often with 2-3mm of gouge. Fractures are closely spaced, on average <10cm separated them. »« gg 2%»« bx 30%»« Brco 68%» « 165.70- 167.90 Carbonaceous mudstone as described; contorted, kinked bands of calcareous mudstone and chert are roughly parallel to core axis and									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-212

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		show weak signs of dextral strain. Limestone fragments have deformed S0 around them - they appear as drop-stones(?). Late stage calcite veining has an affinity for depositional boundaries and irregularities like the limestone fragments. Fibrous calcite growth could easily be measured here with meaning, if the core was oriented. Such a measurement could help to define late-stage stress regime.» « 167.90- 169.30 Medium to coarse-grained limestone clasts, sharp boundaries are associated with pyrite and calcite. » « 169.30- 169.60 Carbonaceous Mudstone » « 169.60- 175.60 upper 0.7m is all fault gouge with remineralized anhydrite-rich bluish surfaces. Broken core pieces show mosaic-style brecciation of pyrite in calcic matrix, in addition to mudstone breccia fragments. Abundant plane-parallel slippage occurs on fault breccia pieces. FLT »« gg 20%»« bx 30%»« Brco 50%» « 175.60- 187.50 Carbonaceous mudstone as described, here with an increase in mm-scale pyrite blebs and stringers that can help define S0. Limestone 'concretions' are conformable to S0, between 3-7cm thick. Calcic and cherty bands show little consistency in geometry. The unit is fairly monotonous and without pyrite blebs and stringers it would appear massive in many sections. » < @ 178.40 defined by laminae S0, tca 84° > < @ 180.00 defined by conformable calcic bands S0, tca 84° > < @ 182.30 defined by pyritic laminae and conformable limestone clasts S0, tca 39° > « 187.50- 189.00 Limestone 'concretion', upper half is fine to medium grained and massive, lower half appears to be highly bioturbated. »									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-212

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
« 189.00- 207.70 Heterogeneous carbonaceous mudstone, mixed zone with calcite veins (3-15cm thick) that brecciate host rock. Abundant soft-sed deformation features, mostly slumping and syn-depositional folding. Limestone 'concretions' are abundant, laminae are convoluted. In some internally brecciated zones the XRF reads up to 0.5% Zn in a point source fashion. Calcite veins are associated with massive pyrite. This interval has an increase in calcic and cherty banding. Numerous stylolites and pressure dissolution seams. Many of the larger calcite veins have been recrystallized and quartz. » « 207.70- 207.90 FLT,secondary anhydrite tends to 'ooze' from gouge»« gg 100%»« bx »«Brco» « 207.90- 212.00 the broken core pieces are mylonitic and developed numerous slick-n-sides, especially where calcareous compent is minor. Increases in calcareous content resist fault straining FLT »« gg 10%»« bx 25%»« Brco 65%» « 212.00- 212.50 Muddy limestone 'concretion' » « 210.50- 211.90 Outer shoulder Sample; please refer to description for interval 207.9-212 for this sample. [Pb: 0.145%; Zn: 0.219%] » « 211.90- 212.50 Inner shoulder Sample; muddy limestone 'concretion' [Pb:0.136%; Zn:0.172%] »											
212.50	236.90	ACTM	633103	212.50	213.20	0.70	0.13	0.44	1.00	20.00	0.30
ACTM – Active Member			633104	213.20	214.30	1.10	1.34	4.25	1.00	130.00	0.32
			633105	214.30	215.30	1.00	1.66	5.15	1.00	130.00	0.32
			633106	215.30	215.60	0.30	0.73	2.14	1.00	50.00	0.34
			633107	215.60	217.10	1.50	1.84	5.81	1.00	150.00	0.32
			633108	217.10	217.60	0.50	2.02	7.31	1.00	290.00	0.28
			633109	217.60	218.00	0.40	1.17	1.91	1.00	60.00	0.61
			633110	218.00	218.80	0.80	3.16	0.91	1.00	30.00	3.47
The ACTM consists of a repetitive, possibly rhythmic, sequence of intercalated carbonaceous mudstone, cherty mudstone, chert and limestone and locally contains economically significant Zn and Pb sulphides (see bold marked facies), mainly in its sections with well developed lamination. Because of its heterogeneity, the member is distinctive and easily identified.											

Selwyn Project Diamond Drill Log

Hole Number:
XYC-212

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
=====			633111	218.00	218.80	0.80	3.61	0.41	1.00	10.00	8.80
			633112	218.80	219.60	0.80	0.06	0.12	1.00	5.00	0.50
The ACTM has 8 different facies:			633113	219.60	220.40	0.80	0.05	0.27	1.00	5.00	0.19
=====			633114	220.40	221.50	1.10	0.20	0.07	1.00	5.00	2.86
			633115	221.50	222.40	0.90	0.06	0.46	1.00	10.00	0.13
- GREY CHERT FACIES: Consists of laminated medium light grey to medium dark grey chert. Mineralization: 95-99% quartz and up to 5% secondary calcite.			633116	222.40	223.00	0.60	0.01	0.08	1.00	5.00	0.13
			633117	223.00	224.10	1.10	0.10	0.07	1.00	5.00	1.43
			633118	224.10	224.70	0.60	0.09	1.11	1.00	30.00	0.08
- WHITISH GREY ZN-PB MUDSTONE FACIES: Is a laminated cherty rock containing up to 70% sulphides. Mineralization: quartz, sphalerite and galena are the major minerals with only minor amounts of pyrite and locally calcite. Sedimentary diagenetic structures are common and well displayed in the facies, such as: lamination, pseudo-beds, calcite nodules & limestone nodules and abundant water escape structures. Most obvious structure in facies is cross-cutting veins containing massive sphalerite and galena with minor pyrite. They range in width from 0.5 to 10mm.			633119	224.70	225.80	1.10	0.04	0.09	1.00	5.00	0.44
			633120	225.80	225.80	0.00	0.01	0.01	1.00	5.00	2.00
			633121	225.80	227.00	1.20	0.17	0.30	1.00	5.00	0.57
			633122	227.00	227.40	0.40	0.33	3.96	1.00	90.00	0.08
			633123	227.40	228.30	0.90	0.15	0.96	1.00	20.00	0.16
			633124	228.30	228.60	0.30	0.29	3.08	2.00	90.00	0.09
			633125	228.60	230.10	1.50	0.03	0.17	1.00	5.00	0.18
			633126	230.10	231.20	1.10	0.09	0.44	1.00	10.00	0.20
			633127	231.20	231.90	0.70	0.30	1.26	2.00	40.00	0.24
- THIN BEDDED CHERTY MUDSTONE FACIES: Consists of rhythmic intercalated laminae of chert, carbonaceous mudstone and minor micrite. This facies contains significant amounts of Zn and Pb sulphides.			633128	231.90	232.70	0.80	0.27	0.65	4.00	20.00	0.42
			633129	232.70	234.20	1.50	0.17	0.64	3.00	20.00	0.27
			633130	234.20	234.20	0.00	0.93	1.31	226.00	90.00	0.71
- CHERTY MUDSTONE FACIES: Consists of a greyish black monotonous siliceous, carbonaceous mudstone. It is most typically found overlying the thin bedded calcareous mudstone facies.			633131	234.20	235.30	1.10	0.14	0.35	4.00	10.00	0.40
			633132	235.30	236.90	1.60	0.03	1.19	2.00	70.00	0.03
- THIN BEDDED CALCAREOUS MUDSTONE FACIES: Consists of laminated carbonaceous mudstone containing 20-40% calcite, 40-55% quartz and 10-20% muscovite. Sulphides occur in laminae. In the XY area it is usually the lowest facies in the section to contain laminated sulphides.											
- CALCAREOUS MUDSTONE FACIES: Consists of grey to greyish black monotonous, calcareous siliceous carbonaceous mudstone. There are no feathery calcite beds or pyrite-calcite blebs in the facies, making it easily distinguishable from											

Selwyn Project Diamond Drill Log

Hole Number:
XYC-212

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		the CCMS. - GRADED LIMESTONE FACIES: Is a laminated argillaceous limestone with intercalated carbonaceous limestone laminae. The main rock type in the facies is laminated limestone with laminae up to 0.1-7mm thick. - LIGHT GREY BASAL LIMESTONE FACIES - LGLS: Consists of laminated argillaceous limestone. In the Anniv area it marks the end of the ACTM. It's not always present in the stratigraphy. - BASAL FACIES: This is a highly contorted and locally foliated carbonaceous mudstone. Unlike the other facies it is not repeated higher in the member. It appears locally to contain the slip zone of a major slump. The facies has only been observed in the YX area. It is 0.1-2m thick. The facies consists of massive carbonaceous siliceous mudstone with lenses and laminae of contorted, slightly carbonaceous chert. « 212.50- 213.20 Carbonaceous and calcareous mudstone to muddy limestone. Abundant pseudotachylite and slick-n-lines. Some broken core pieces show weak laminations recrystallized quartz and calcite exposed on breccia pieces. FLT » »« gg 15%»« bx 50%»« Brco 35%» «[Pb: 0.369%; Zn: 0.951%] » « 213.20- 214.30 Carbonaceous and calcareous mudstone to muddy limestone. Abundant calcite veinlets, medium to dark grey in colour. Recrystallized quartz-calcite. FLT » »« gg 15%»« bx 35%»« Brco 50%»«[Pb: 2.15%; Zn: 2.66%] » « 214.30- 215.30 Intercalated muddy limestone with laminated carbonaceous and calareous mudstone. Abundant irregular calcite veinlets. Limestone concretions on cm-scale, soft-sed slumping, and minor fragmental limestone. Still in a zone that is affected by faulting with some mylonitic mudstone near the middle of interval.»«[Pb: 2.63%; Zn: 3.86%]» « 215.30- 215.60 Muddy limestone, massive to weakly laminated, intercalated with minor laminated calcareous mudstone. Deformed calcite +/-									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-212

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		quartz veins and remineralized stylolites. Occassionally in the limestone there are sulphide-rich laminae that have Zn-enrichments »«[Pb: 0.518%; Zn: 1.06%]» « 215.60- 217.10 Interval of calcareous laminated mudstone, typical soft sed deformation features. Galena mineralization is commonly remobilized along depositional boundaries and in veinlets aswell. Sphalerite concentrates in laminae locally. Limestone fragments 2-15mm di. are often associated with pyrite. Some laminae boundaries are replaced by calcite and quartz presumably replacing stylolites. » «[Pb: 1.35%; Zn: 4.3%] » « 217.10- 217.60 Massive to weakly laminated muddy limestone with interstitial sphalerite and remobilized galena. Sphalerite concentrations vary significantly from 1% to >50%, especially on freshly broken surfaces. Sphalerite is also concentrated in blebs within calcite veins. The lower part of the interval shows ~50% mud laminae to limsestone laminae. »«[Pb: 2.71%; Zn: 4.97%] » « 217.60- 218.00 Laminated veru calcareous mudstone, highly variable laminae, some enriched with sulphides including pyrite and minor sphalerite. Calcite veining is minor. »«[Pb: 0.402%; Zn: 1.26%] » « 218.00- 218.80 Brecciated zone of intercalated laminated mudstone with limestone 'concretions'. Pyritic laminae are common and often associated with sphalerite. Galena tends to occur as irregular and often discontinuous wispy veinlets. Recrystallized quartz-calcite is a common feature. Some <1mm zones of gouge accompany pseudotachylite on slippage surfaces.»«[Pb: 2.47%; Zn: 2.62%] » « 218.80- 219.60 Heavily fractured calcareous mudstone, minor limestone 'concretions'. Recrystallized quartz-calcite veins and blow-outs. Rock becomes more competent near bottom of interval, also there is am increase in calci veins. »«[Pb: 0.139%; Zn: 0.154%] » « 219.60- 220.40 Massive to weakly laminated muddy limestone with very									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-212

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		minor patches of intercalated sphalerite. Elongate limestone 'concretions' near upper interval. Thin discordant but systematic calcite veinlets, possibly defining a foliation (S1)» «[Pb: 0.111%; Zn: 0.124%] » < @ 219.60 calcite veilet defined foliation S1, 40 tca > « 220.40- 221.50 Medium grey, weakly to moderately laminated. Pervasive specular pyrite. Elongate limestone 'concretions' with rounded boundaries. Wispy calcite helps to define S1(?). Calcite + quartz remineralized stylolites and veins. No visible concentrations of base metals.»«[Pb: 0.155%; Zn: 0.127%] » « 221.50- 222.40 Laminated carbonaceous mudstone with intercalated calcic laminae. cm-scale limestone 'concretions' as described. Pyrite is disseminated in trace amounts and also remobilized into wispy blebs with washed out boundaries. Recrystallized quartz-calcite »«[Pb: 0.258%; Zn: 0.430%] » « 222.40- 223.00 Intercalated weakly calcareous, carbonaceous mudstone with strongly calcareous laminated mudstone. Systematic weinlets of calcite continue to define S1, quartz is associated with calcite in subordinate amounts»«[Barren] » < @ 222.40 defined by cal-qy veinlets which may be remineralizing along foliation plane S1, tca 27° > « 223.00- 224.10 Finely laminated calcareous mudstone. Many pyritic rich laminae as well as disseminated, blebby and patchy pyrite. Upper part of interval has 10cm thick calcite- quartz vein with abundant brecciated mudstone encorporated and patches of massive pyrite »«[Pb: 0.103%; Zn: 0.062%] » < @ 223.00 defined by laminae S0, tca 53° > « 224.10- 224.70 Weakly calcareous, carbonaceous laminated mudstone intercalated with limestone 'concretions'. Recrystallized quartz-calcite.									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-212

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		Abundant cuspsate, square and irregular stylolites, typically not remineralized. Wispy and spotted calcite. Pyrite concentrates along the edges of limestone 'concretions' »«[Pb: 0.270%; Zn: 0.631%] » « 224.70- 225.80 Laminated muddy limestone, systematic wispy calcite veins may help to define S1. Blebbpy pyrite (<1%). Wavy irregular laminae are 2-6mm thick, commonly associated with irregular stylolites marking major depositional boundaries, some stylolites have been remineralized with cal-quartz. Limestone 'concretions' deform S0 and actually look like Clasts! I think they are clasts, not concretions - this is why I put 'quotes' around the word concretion. »«[Zn: 0.135%] » ◁ @ 225.30 defined by wispy systematic calcic veinlets. S1, tca 45° ▷ « 225.80- 227.00 Moderately to weakly calcareous laminated mudstone, intercalated with minor amounts of muddy laminated limestone. Laminae are irregular. Stylolites separate depositional boundaries. Limestone 'concretions' host pyrite internally and near margins. There are darker carbonaceous layers 3-15cm thick that show slight increases in base metal mineralization. »«[Pb: 0.335%; Zn: 0.353%] » « 227.00- 227.40 Laminated, slightly calcareous mudstone, pyritic laminae and pervasive pyrite dissemination (<1%). Limestone 'concretions' as described . Total sulphide content is estimated at 5-7%»«[Pb: 0.735%; Zn: 2.53%] » « 227.40- 228.30 Heterogeneous interval, lithologies are too discontinuous to break up sample. Intercalated laminated coarse-grained limestone with massive to weakly laminated mustone and calcareous mudstone host to numerous calcite-quartz recrystallized veins. Pyrite blow-outs occur in massive zones with calcite-quartz. There are at least two generations of calcite veining. One stage is conformable to depositional boundaries and stylolites, the other is represented by later-stage tension gashes. »«[Pb: 0.299%; Zn: 0.868%] » « 228.30- 228.60 Laminated calcareous mudstone, abundant syndepositional									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-212

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		deformation structures, typical and as described. Elongated limestone 'concretions', blebs of pyrite with calcite-quartz»«[Pb: 0.545%; Zn: 2.35%] » « 228.60- 230.10 Intercalated laminated calcareous mudstone with thickly laminated muddy limestone. Pyritic laminae 1-6mm thick occur in mudstone. Abundant calcite-quartz veining throughout. Laminae are wavy and irregular between depositional boundaries. Minor blebs of massive pyrite up to 10mm diameter, often associated with calcite-quartz. Veining typically occurs at low oblique angle to S0.»«[Pb: 0.077%; Zn: 0.158%] » « 230.10- 231.20 Finely laminated muddy limestone to strongly calcareous mudstone. Medium to light grey in colour. Occasional vblow-outs of pyrite + quartz-calcite are roughly conformable to S0. Numerous thin (<2mm) wispy calcite veinlets are systematic, this may help define an S1. S0 is highly variable. No visible mineralization.»«[Pb: 0.253%; Zn: 0.188%] » < @ 230.80 defined by wispy systematic calcite veinlets S1, tca 42° > « 231.20- 231.90 Laminated very calcareous mudstone with sphalerite enriched pyrite laminae. Laminated muddy limestone clasts/fragments. Blebs of pyrite +/- calcite. Recrystallized quartz-calcite veins as well as calcite-rich laminae and cherty laminae.»«[Pb: 0.252%; Zn: 1.01%] » « 231.90- 232.70 Laminated, moderately calcareous mudstone. Massive pyrite layer ~6cm thick is barren of base metals and later-stage partially brecciated by calcite-quartz. Extensional tension hgashes become numerous in one depositional layer ~20cm thick, coincides with a decrease in calcareous content »«[Pb: 0.327%; Zn: 0.478%] » « 232.70- 234.20 MAssive to weakly laminated carbonaceous mudstone with moderate calcareous content in upper 30cm of interval. Pyritic bands up to 10cm thick, later brecciated by calcite-quartz/. Pseudotachylite developes on fracture surfaces along with slick-n-lines.» «[Pb: 0.193%; Zn: 0.415%] »									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-212

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		« 234.20- 235.30 Carbonaceous mudstone, abundant pseudotachylite, slick-n-lines and recrystallized quartz-calcite. Lower part of interval shows all the Brco and appears to be failing along weakly defined S0, with <2mm gouge between each piece. Irregular calcite+quartz veins are common. FLT »« gg 10%»« bx 50%»« Brco 40%» «[Pb: 0.269%; Zn: 0.302%] »									
		« 235.30- 236.90 Faulted mix of ACTM and CCMS, lots of secondary remineralization on broken surfaces (talc?). Very carbonaceous. FLT »« gg 45%»« bx 45%»« Brco 10%»«[Pb: 0.104%; Zn: 0.448%] »									
236.90	297.10	CCMS	633133	236.90	237.90	1.00	0.01	0.26	1.00	20.00	0.04
		CCMS – Calcareous Mudstone	633134	237.90	238.80	0.90	0.01	0.01	1.00	20.00	2.00
		Massive, calcareous, carbonaceous, dark grey mudstone. Most of the member is massive, but rare poorly defined bedding and pyrite-calcite micro-concretions are present. Most diagnostic structures are feathery calcite beds (=thin calcite-cemented concretions, many of them contain pyrite cores) and calcite pseudo-beds (= fibrous calcite vein parallel to bedding).									
		« lm ca 5.00-10.00mm », « nodules py -3.00% 2.00-20.00mm »,									
		« General description of entire interval. Dark grey to black monotonous, weakly calcareous mudstone with abundant wispy calcite veinlets which help to define a weak lamination. Some sections are massive, mm-scale pyrite blebs occur with clacite and quartz. Some pyrite-rich laminae, although these are minor. Many small fault zones <10-15cm, the larger of which have been separated as intervals. Near bottom of hole quartz-calcite veins 10-20cm thick incorporate breccia fragments of host mudstone. Structural deformation features are largely absent. Pyrite also forms discontinuous wormy bands <1-3mm long. Rock is fissile and has plane-parallel failure often with S0. »									
		« 236.90- 237.90 Black carbonaceous, monotonous mudstone, very minor <2mm pyritic laminae and rare weakly calcic bands are the only indication of a lamination. »«[Barren]»									

Diamond Drill Log

Comprehensive Report for Hole:

XYC-211

Hole No.: XYC-211	Depth: 293.00 m	Horizontal Length: 0.00 m	Project: 1710
Location Data:			
Property:	Selwyn Project	Claim Name:	X 14
Mining District:	Selwyn Basin	Grant Number:	Y 64539
Province/Territory:	Yukon		
UTM Co-Ordinates & Altitude of Drill Hole Collar:			
UTM Easting:	489045.82 m	True Azimuth:	205.0 °
UTM Northing:	6926159.92 m	Hole Angle:	-65.0 °
Elevation (m):	1607.18 m	NTS Name:	Placer Creek
		NTS Number:	105L06
Grid Co-Ordinates of Drill Hole Collar:			
Grid Easting (m):	0.00 m	Grid Name:	HP 06
Grid Northing (m):	0.00 m	Grid Type:	100m
Grid Azimuth:	265.0 °		
Dimond Drilling Contract:			
Drilled By:	CY-01	Date Drilling Start:	09/20/2010
		Date Finish:	09/26/2010
Diamond Drill Core:			
Logged By:	Jelle De Bruyckere	Date Logging Start:	09/30/2010
		Date Finish:	10/02/2010
Legend for Core Logging Codes: PAX			
Core Size:	NQ	Cemented:	Yes
Casing Depth:	9.60 m	Casing Pulled:	Yes
Water Depth:	0.00 m	Overburden Depth:	9.60 m
Level:			
Section:		Drift:	

Selwyn Project

Diamond Drill Log

Survey Data for Hole

XYC-211

Hole Comments:

Mon, Sep 20 --- Lined up and 30 ft of casing in the ground. Had some waterline problems through the night.

=====

Tue, Sep 21 --- 9.1 m of casing is down. Drilling to a depth of 60 m in USMS(?). No issues to report.

=====

Wed, Sep 22 --- "Currently in USMS at 107 m. Core is brought down when time and personnel are available."

=====

Thu, Sep 23 --- Expecting to see more core later today if they can make it down the road.

=====

Fri, Sep 24 ---

=====

Sat, Sep 25 --- No new core this am.

=====

Sun, Sep 26 --- Currently in CCMS at 297 m. Shutting down.

<i>Depth</i>	<i>Dip</i>	<i>Azimuth</i>
0.00	-65.0	205.0
33.00	-64.1	209.0
83.00	-62.3	212.3
133.00	-61.7	209.2
183.00	-59.6	213.3
233.00	-57.9	205.5
284.00	-55.0	205.5

Selwyn Project Diamond Drill Log

Hole Number:
XYC-211

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
0.00	9.60	OVBR									
9.60	24.90	FLMD									
FLMD – Flaggy Mudstone Formation Dark grey mudstone in the upper portions of the unit grading into light grey mudstone to siltstone. Contains abundant wispy bioturbation which ranges from randomly-oriented at the top of the unit to bedding-parallel throughout the majority of the unit. Darker upper section has a strong fetid odour along broken surfaces. « btrb 0.10-2.00cm », « cg xtl crns ca 1.00-5.00% 5.00-150.00cm », « crns py 1.00-5.00% 0.10-0.50mm » < @ 11.90 S0 defined by bioturbations S0 tca 41° > < @ 12.80 S0 defined by bioturbations S0 tca 47° > < @ 19.00 S0 defined by bioturbations S0 tca 50° >											
24.90	135.60	USMS	632851	33.50	33.80	0.30	0.07	0.01	1.00	5.00	7.00
USMS – Upper Siliceous Mudstone Consists of interlaminated dark grey to black mudstone and light to medium grey chert. Regionally, a 1m thick graptolite zone occurs 15m below the top of the upper unit, this is usable as a horizon. The USMS is divided into 3 units. The Lower Unit contains abundant limestone concretions and Galena and sphalerite micro-concretions occur locally near the base of this unit. « gra , lm chrt -20.00% », « cg xtl sph crns ca 5.00-20.00cm », « bed chrt 10.00-15.00% » < @ 27.20 S0 defined by parallel chert bands S0 tca 63° > < @ 33.00 S0 defined by parallel chert bands S0 tca 81° > « 33.80- 34.80 Mineralized calcareous mudstone with well developed lamination. Mineralization: 8% Zn & 2% Pb. » < @ 45.30 S0 defined by parallel chert bands S0 tca 72° > < @ 59.40 S0 defined by parallel chert bands S0 tca 80° >			632852	33.80	34.30	0.50	0.86	7.80	6.00	220.00	0.11
			632853	34.30	34.80	0.50	2.36	9.51	7.00	270.00	0.25
			632854	34.80	35.20	0.40	0.09	0.80	1.00	20.00	0.11
			632855	133.10	134.00	0.90	0.06	0.22	1.00	5.00	0.27
			632856	134.00	135.60	1.60	0.02	0.08	2.00	5.00	0.25

Selwyn Project Diamond Drill Log

Hole Number:
XYC-211

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
< @ 65.00	S0 defined by parallel chert bands S0 tca 63°	>									
< @ 82.70	S0 defined by parallel chert bands & lenticular pyrite nodules S0 tca 70°	>									
< @ 111.60	S0 defined by parallel chert bands & lenticular pyrite nodules S0 tca 80°	>									
135.60	145.70	ACTM	632857	135.60	137.40	1.80	2.89	8.57	4.00	410.00	0.34
ACTM – Active Member			632858	137.40	139.00	1.60	0.53	3.16	1.00	90.00	0.17
			632859	139.00	139.50	0.50	2.05	9.97	3.00	280.00	0.21
			632860	139.50	140.30	0.80	1.16	4.98	1.00	140.00	0.23
			632861	139.50	140.30	0.80	1.05	4.68	2.00	120.00	0.22
			632862	140.30	140.70	0.40	2.80	11.14	3.00	350.00	0.25
			632863	140.70	141.80	1.10	0.15	0.07	1.00	5.00	2.14
			632864	141.80	142.80	1.00	0.43	0.03	1.00	5.00	14.33
			632865	142.80	143.90	1.10	0.05	0.04	1.00	5.00	1.25
			632866	143.90	145.70	1.80	0.09	0.04	1.00	5.00	2.25
The ACTM consists of a repetitive, possibly rhythmic, sequence of intercalated carbonaceous mudstone, cherty mudstone, chert and limestone and locally contains economically significant Zn and Pb sulphides (see bold marked facies), mainly in its sections with well developed lamination. Because of its heterogeneity, the member is distinctive and easily identified. ===== The ACTM has 8 different facies: ===== - GREY CHERT FACIES: Consists of laminated medium light grey to medium dark grey chert. Mineralization: 95-99% quartz and up to 5% secondary calcite. - WHITISH GREY ZN-PB MUDSTONE FACIES: Is a laminated cherty rock containing up to 70% sulphides. Mineralization: quartz, sphalerite and galena are the major minerals with only minor amounts of pyrite and locally calcite. Sedimentary diagenetic structures are common and well displayed in the facies, such as: lamination, pseudo-beds, calcite nodules & limestone nodules and abundant water escape structures. Most obvious structure in facies is cross-cutting veins containing massive sphalerite and galena with minor pyrite. They range in width from 0.5 to 10mm. - THIN BEDDED CHERTY MUDSTONE FACIES: Consists of rhythmic intercalated laminae of chert, carbonaceous mudstone and minor micrite. This facies contains significant amounts of Zn and Pb sulphides.											

Selwyn Project Diamond Drill Log

Hole Number:
XYC-211

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		- CHERTY MUDSTONE FACIES: Consists of a greyish black monotonous siliceous, carbonaceous mudstone. It is most typically found overlying the thin bedded calcareous mudstone facies. - THIN BEDDED CALCAREOUS MUDSTONE FACIES: Consists of laminated carbonaceous mudstone containing 20-40% calcite, 40-55% quartz and 10-20% muscovite. Sulphides occur in laminae. In the XY area it is usually the lowest facies in the section to contain laminated sulphides. - CALCAREOUS MUDSTONE FACIES: Consists of grey to greyish black monotonous, calcareous siliceous carbonaceous mudstone. There are no feathery calcite beds or pyrite-calcite blebs in the facies, making it easily distinguishable from the CCMS. - GRADED LIMESTONE FACIES: Is a laminated argillaceous limestone with intercalated carbonaceous limestone laminae. The main rock type in the facies is laminated limestone with laminae up to 0.1-7mm thick. - LIGHT GREY BASAL LIMESTONE FACIES - LGLS: Consists of laminated argillaceous limestone. In the Anniv area it marks the end of the ACTM. It's not always present in the stratigraphy. - BASAL FACIES: This is a highly contorted and locally foliated carbonaceous mudstone. Unlike the other facies it is not repeated higher in the member. It appears locally to contain the slip zone of a major slump. The facies has only been observed in the YX area. It is 0.1-2m thick. The facies consists of massive carbonaceous siliceous mudstone with lenses and laminae of contorted, slightly carbonaceous chert. « 135.60- 140.70 A 5.1m long broken up mineralized section. Because it's broken up and because it's a mix of diverse and short facies, I decided to log it as one range feature. It contains siliceous laminated mudstone, calcareous									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-211

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		high grade mudstone & carbonaceous barren mudstone. » « 140.70- 145.70 Mainly bedded limestone and calcareous mudstone. Mostly barren. One visible galena stringer, 4cm long and 3mm wide. »									
145.70	293.00	CCMS	632867	145.70	146.80	1.10	0.01	0.01	1.00	5.00	2.00
		CCMS – Calcareous Mudstone	632868	146.80	147.10	0.30	0.01	0.01	1.00	5.00	2.00
			632869	147.10	147.50	0.40	0.01	0.01	1.00	5.00	2.00
		Massive, calcareous, carbonaceous, dark grey mudstone. Most of the member is massive, but rare poorly defined bedding and pyrite-calcite micro-concretions are present. Most diagnostic structures are feathery calcite beds (=thin calcite-cemented concretions, many of them contain pyrite cores) and calcite pseudo-beds (= fibrous calcite vein parallel to bedding). « lm ca 5.00-10.00mm », « nodules py -3.00% 2.00-20.00mm » « 145.70- 293.00 The rocks do not appear to be typical CCMS, but rather USMS or BSSM resembling rocks, although not completely. As described in the range features below, the section resembling USMS does not have the typical spherical radiating carbonate concretions and the mudstone is mainly calcareous. The lower section resembling BSSM is calcareous, has a moderately developed bedding, has no bioturbations, but at the same time doesn't look dark enough to be CCMS. It has barely graphite on the fracture surfaces. Not enough pyrite and too calcareous to be PSMS. Also, there is no fault observed between the so called USMS section and the BSSM section, which would have been necessary if the ranges were really the units USMS and BSSM. » « 146.00- 146.90 Flt »« Flt gg 60% (majority is washed away)»« Flt bx 20%» « Brco 10%» « 146.90- 207.00 Rocks resemble USMS, but not completely, as the core is partially calcareous, partially siliceous and the spherical carbonate concretions are missing. Chert bands and thin bands of	632870	147.50	147.50	0.00	0.01	0.01	1.00	5.00	2.00

Selwyn Project Diamond Drill Log

Hole Number:
XYC-211

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		calcite+/-quartz+/-pyrite are present, and sometimes locally deformed. Minor pyrite concretions are also present in the rock. » ◁ @ 175.00 S0 defined by faint beds S0 tca 64° ▷ ◁ @ 190.60 S0 defined by thin beds and minor parallel pyrite bands in calcareous mudstone S0 tca 55° ▷ « 207.00- 293.00 The rocks in this section resemble BSSM, but not completely. Medium grey calcareous mudstone with a moderately well developed bedding. The bedding is defined by parallel faint/thin pyrite bands or parallel thin lenticular pyrite nodules. » ◁ @ 216.20 S0 defined by parallel faint pyrite beds S0 tca 58° ▷ ◁ @ 223.50 S0 defined by parallel faint pyrite beds S0 tca 66° ▷ ◁ @ 225.30 S0 defined by parallel faint pyrite beds S0 tca 67° ▷ ◁ @ 235.20 S0 defined by parallel faint pyrite beds S0 tca 69° ▷ ◁ @ 238.40 S0 defined by thin parallel calcite beds S0 tca 64° ▷ ◁ @ 247.60 S0 defined by parallel faint pyrite beds S0 tca 49° ▷ ◁ @ 251.20 S0 defined by parallel faint pyrite beds S0 tca 62° ▷ ◁ @ 259.90 S0 defined by parallel faint pyrite beds S0 tca 70° ▷ ◁ @ 270.00 S0 defined by parallel faint pyrite beds S0 tca 50° ▷ ◁ @ 272.20 S0 defined by parallel faint pyrite beds S0 tca 54° ▷ ◁ @ 283.80 S0 defined by parallel faint pyrite beds S0 tca 51° ▷ ◁ @ 287.00 S0 defined by parallel faint pyrite beds S0 tca 49° ▷									
293.00	293.00	EOH									

Diamond Drill Log

Comprehensive Report for Hole:

XYC-210

Hole No.: XYC-210	Depth: 335.10 m	Horizontal Length: 0.00 m	Project: 1710
Location Data:			
Property:	Selwyn Project	Claim Name:	X 11
Mining District:	Selwyn Basin	Grant Number:	Y 64536
Province/Territory:	Yukon		
UTM Co-Ordinates & Altitude of Drill Hole Collar:			
UTM Easting:	488496.00 m	True Azimuth:	34.0 °
UTM Northing:	6926586.00 m	Hole Angle:	-85.0 °
Elevation (m):	1604.00 m	NTS Name:	Placer Creek
		NTS Number:	105L06
Grid Co-Ordinates of Drill Hole Collar:			
Grid Easting (m):	0.00 m	Grid Name:	HP 06
Grid Northing (m):	0.00 m	Grid Type:	100m
Grid Azimuth:	94.0 °		
Dimond Drilling Contract:			
Drilled By:	NL-02	Date Drilling Start:	09/17/2010
		Date Finish:	09/22/2010
Diamond Drill Core:			
Logged By:	Jelle De Bruyckere / Kate	Date Logging Start:	09/21/2010
		Date Finish:	10/03/2010
Legend for Core Logging Codes: PAX			
Core Size:	NQ3	Cemented:	Yes
Casing Depth:	11.30 m	Casing Pulled:	Yes
Water Depth:	0.00 m	Overburden Depth:	11.30 m
Level:	Section:	Drift:	

Selwyn Project

Diamond Drill Log

Survey Data for Hole

XYC-210

Hole Comments:

Fri, Sep 17 --- Got 10 m of casing down.
=====

Sat, Sep 18 --- No issues to report. In Flaggy Mudstone at 59.4 m. Competent rock. Missed 50 m Flexit, doing it first thing when they get up there (60 m).
=====

Sun, Sep 19 --- Flaggy ends at approx. 120 m. Into Upper Siliceous. Good drilling, no issues.
=====

Mon, Sep 20 --- Still in USMS, no issues to report. Current depth 241 m.
=====

Tue, Sep 21 --- ACTM from approx. 239 m to 282 m. Rubble/fracture below 291.6 m to their current depth of 295.4 m in CCMS. David plans to have them drill approx. Another 25 m.
=====

Wed, Sep 22 --- Currently in CCMS at 335.1 m. Hole shut down, drill to move to setup #26.

<i>Depth</i>	<i>Dip</i>	<i>Azimuth</i>
0.00	-85.0	34.0
50.00	-85.2	34.3
103.00	-84.6	32.9
150.00	-85.5	40.5
200.00	-83.8	43.1
252.60	-83.9	42.3
302.00	-84.4	44.6

Selwyn Project Diamond Drill Log

Hole Number:
XYC-210

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
0.00	11.30	OVBR <i>First part of the log is Kate Cameron's log.</i>									
11.30	32.80	BSSM <i>BSSM – Backside Siliceous Mudstone</i> <i>Devonian Siliceous Mudstone – Upper Chert Formation</i> <i>Greyish black laminated chert and siliceous mudstone. Randomly-oriented to bedding-parallel bioturbation is common in the bottom of the unit. « lm chrt 75.00-95.00% », « btrb 0.10-2.00cm »</i> <i>« 11.30- 32.80 Siliceous mudstone. Well fractured core above 24m. Calcite+/-pyrite veins, 3mm to 2cm wide. Weakly laminated black mudstone, no distortion. »</i>									
32.80	145.20	FLMD <i>FLMD – Flaggy Mudstone Formation</i> <i>Dark grey mudstone in the upper portions of the unit grading into light grey mudstone to siltstone. Contains abundant wispy bioturbation which ranges from randomly-oriented at the top of the unit to bedding-parallel throughout the majority of the unit. Darker upper section has a strong fetid odour along broken surfaces. « btrb 0.10-2.00cm », « cg xtl crns ca 1.00-5.00% 5.00-150.00cm », « crns py 1.00-5.00% 0.10-0.50mm »</i> <i>« 32.80- 142.20 Medium grey siliceous mudstone with abundant quartz veins, ranging from mm scale to 3cm wide. The colour of the core lightens with depth to very light grey below 35m. Quartz veins disappeared at this point. Unit very silicified + flaggy bedding. Contains sections of darker, less disturbed siliceous mudstone. »</i> <i>« 59.00- 73.00 Quartz veins (10-30cm long) occur often; sometimes associated with pyrite. »</i> <i>« 60.00- 60.30 Quartz+/-pyrite veins/blebs »</i>									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-210

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		« 71.30- 74.10 Flt »« Flt gg 10%»« Flt bx 80%»« Brco 10%» < @ 96.00 Shear defined by dark layers of flags - Shear bedding 30 > < @ 107.70 S0 tca 15° > < @ 123.20 30 cm of fine pyrite blebs > < @ 130.70 S0 tca 12° > < @ 139.10 S0 tca 17° >									
145.20	243.00	USMS	634501	241.30	241.80	0.50	0.01	0.25	1.00	5.00	0.04
USMS – Upper Siliceous Mudstone			634502	241.80	243.00	1.20	0.02	0.01	1.00	5.00	4.00
Consists of interlaminated dark grey to black mudstone and light to medium grey chert. Regionally, a 1m thick graptolite zone occurs 15m below the top of the upper unit, this is usable as a horizon. The USMS is divided into 3 units. The Lower Unit contains abundant limestone concretions and Galena and sphalerite micro-concretions occur locally near the base of this unit. « gra , lm chrt -20.00% », « cg xtl sph crns ca 5.00-20.00cm », « bed chrt 10.00-15.00% » « 145.20- 243.00 Undeformed beds. Cherty, wormy bedding, thin calcareous stringers along foliation/bedding. Very siliceous. Some carbonaceous sections. » < @ 151.40 S0 tca 25° > « 154.30- 154.60 Carb. vein » « 156.00- 156.90 Flt »« Flt gg 0°»« Flt bx 50%»« Brco 50%»« Very carbonaceous » < @ 161.80 S0 tca 20° > FROM HERE ON IT'S JELLE'S LOG. Classic USMS.											

Selwyn Project Diamond Drill Log

Hole Number:
XYC-210

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
< @ 177.10 S0 defined by chert band S0 tca 30° >											
< @ 184.10 S0 defined by chert band S0 tca 22° >											
< @ 196.40 S0 defined by chert band S0 tca 21° >											
< @ 200.40 S0 defined by chert band S0 tca 21° >											
< @ 232.90 S0 defined by chert band S0 tca 50° >											
< @ 233.10 S0 defined by chert band S0 tca 42° >											
243.00 289.30 ACTM			634503	243.00	243.90	0.90	0.12	0.29	1.00	10.00	0.41
ACTM – Active Member			634504	243.90	245.00	1.10	0.02	0.32	1.00	10.00	0.06
			634505	245.00	245.80	0.80	3.09	10.60	4.00	420.00	0.29
			634506	245.80	246.50	0.70	3.20	10.30	4.00	400.00	0.31
			634507	246.50	247.90	1.40	0.52	1.08	1.00	40.00	0.48
			634508	247.90	248.90	1.00	1.53	10.18	3.00	260.00	0.15
			634509	248.90	250.10	1.20	0.25	0.93	1.00	30.00	0.27
			634510	250.10	251.50	1.40	0.17	1.32	1.00	40.00	0.13
			634511	250.10	251.50	1.40	0.27	2.31	1.00	60.00	0.12
			634512	251.50	252.60	1.10	0.06	0.98	1.00	30.00	0.06
			634513	252.60	254.00	1.40	0.34	1.02	1.00	30.00	0.33
			634514	254.00	255.10	1.10	3.20	18.67	4.00	490.00	0.17
			634515	255.10	255.80	0.70	1.15	1.00	1.00	30.00	1.15
			634516	255.80	256.00	0.20	4.91	16.00	4.00	460.00	0.31
			634517	256.00	256.60	0.60	0.03	0.02	1.00	5.00	1.50
			634518	256.60	257.60	1.00	0.81	4.34	1.00	130.00	0.19
			634519	257.60	258.70	1.10	0.75	5.26	1.00	140.00	0.14
			634520	258.70	258.70	0.00	0.01	0.02	1.00	5.00	0.50
			634521	258.70	259.50	0.80	0.82	5.73	1.00	150.00	0.14
			634522	259.50	260.20	0.70	1.40	7.42	1.00	200.00	0.19
			634523	260.20	261.10	0.90	0.89	0.77	1.00	20.00	1.16
			634524	261.10	262.00	0.90	0.36	2.45	1.00	70.00	0.15
			634525	262.00	262.30	0.30	3.64	18.49	4.00	730.00	0.20
			634526	262.30	263.20	0.90	2.27	5.41	1.00	170.00	0.42
			634527	263.20	263.60	0.40	9.99	30.44	8.00	820.00	0.33
			634528	263.60	264.10	0.50	15.06	29.72	8.00	1120.00	0.51

Selwyn Project Diamond Drill Log

Hole Number:
XYC-210

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
laminae of chert, carbonaceous mudstone and minor micrite. This facies contains significant amounts of Zn and Pb sulphides. - CHERTY MUDSTONE FACIES: Consists of a greyish black monotonous siliceous, carbonaceous mudstone. It is most typically found overlying the thin bedded calcareous mudstone facies. - THIN BEDDED CALCAREOUS MUDSTONE FACIES: Consists of laminated carbonaceous mudstone containing 20-40% calcite, 40-55% quartz and 10-20% muscovite. Sulphides occur in laminae. In the XY area it is usually the lowest facies in the section to contain laminated sulphides. - CALCAREOUS MUDSTONE FACIES: Consists of grey to greyish black monotonous, calcareous siliceous carbonaceous mudstone. There are no feathery calcite beds or pyrite-calcite blebs in the facies, making it easily distinguishable from the CCMS. - GRADED LIMESTONE FACIES: Is a laminated argillaceous limestone with intercalated carbonaceous limestone laminae. The main rock type in the facies is laminated limestone with laminae up to 0.1-7mm thick. - LIGHT GREY BASAL LIMESTONE FACIES - LGLS: Consists of laminated argillaceous limestone. In the Anniv area it marks the end of the ACTM. It's not always present in the stratigraphy. - BASAL FACIES: This is a highly contorted and locally foliated carbonaceous mudstone. Unlike the other facies it is not repeated higher in the member. It appears locally to contain the slip zone of a major slump. The facies has only been observed in the YX area. It is 0.1-2m thick. The facies consists of massive carbonaceous siliceous mudstone with lenses and laminae of contorted, slightly carbonaceous chert. « 243.00- 245.00 Barren siliceous, locally cherty, mudstone. One ellipse			634529	264.10	264.60	0.50	10.41	13.64	3.00	590.00	0.76
			634530	264.60	264.60	0.00	1.45	4.40	31.00	270.00	0.33
			634531	264.60	265.30	0.70	11.91	18.49	5.00	610.00	0.64
			634532	265.30	265.90	0.60	3.96	15.77	1.00	390.00	0.25
			634533	265.90	266.50	0.60	6.60	21.49	3.00	570.00	0.31
			634534	266.50	266.90	0.40	4.68	24.07	5.00	620.00	0.19
			634535	266.90	267.30	0.40	6.11	39.12	11.00	1030.00	0.16
			634536	267.30	268.30	1.00	2.72	3.60	1.00	90.00	0.76
			634537	268.30	269.00	0.70	10.61	27.49	4.00	790.00	0.39
			634538	269.00	269.10	0.10	2.04	9.28	3.00	260.00	0.22
			634539	269.10	269.60	0.50	6.90	26.32	3.00	760.00	0.26
			634540	269.60	269.90	0.30	4.13	33.99	8.00	950.00	0.12
			634541	269.60	269.90	0.30	4.32	33.12	7.00	940.00	0.13
			634542	269.90	271.10	1.20	2.69	7.38	1.00	200.00	0.36
			634543	271.10	271.70	0.60	3.58	16.98	1.00	510.00	0.21
			634544	271.70	272.10	0.40	4.60	22.43	1.00	710.00	0.21
			634545	272.10	272.90	0.80	0.84	3.55	1.00	110.00	0.24
			634546	272.90	274.50	1.60	0.02	0.04	1.00	5.00	0.50
			634547	274.50	276.00	1.50	0.03	0.02	1.00	5.00	1.50
			634548	276.00	277.00	1.00	0.17	0.91	1.00	20.00	0.19
			634549	277.00	278.30	1.30	0.10	0.29	1.00	5.00	0.34
			634550	278.30	278.30	0.00	0.01	0.01	1.00	5.00	2.00
			634551	278.30	279.30	1.00	0.37	0.35	1.00	10.00	1.06
			634552	279.30	280.40	1.10	0.13	0.54	1.00	20.00	0.24
			634553	280.40	281.50	1.10	0.03	0.10	1.00	5.00	0.30
			634554	281.50	282.60	1.10	0.39	0.92	1.00	20.00	0.42
			634555	282.60	283.50	0.90	0.18	0.84	3.00	30.00	0.21
			634556	283.50	285.60	2.10	0.14	0.63	1.00	20.00	0.22
			634557	285.60	286.60	1.00	0.14	0.13	1.00	5.00	1.08
			634558	286.60	287.60	1.00	0.01	0.01	1.00	5.00	2.00
			634559	287.60	288.60	1.00	0.01	0.01	1.00	5.00	2.00
			634560	288.60	288.60	0.00	5.95	6.74	68.00	190.00	0.88
			634561	288.60	289.30	0.70	0.01	0.01	1.00	5.00	2.00

Selwyn Project Diamond Drill Log

Hole Number:
XYC-210

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		shaped 'nodule' with disseminated sphalerite in it. This 40mm long and 10mm wide nodule has 7% Zn. »									
		« 245.00- 246.50 Mineralized siliceous mudstone with a well developed lamination. Visible galena stringers and sphalerite laminae/bands. Mineralization: 8% Zn & 5% Pb »									
		« 246.50- 247.90 Bedded limestone with minor mineralization: 0.7% Zn & 0.8% Pb. »									
		« 247.90- 248.90 Mineralized siliceous mudstone with a moderately to well developed lamination. Mineralization: 6% Zn & 1.5% Pb. »									
		« 248.90- 250.10 Mainly limestone, with minor pyrite, sphalerite and galena. Mineralization: 0.8% Zn & 0.8% Pb. »									
		« 250.10- 251.50 Poorly mineralized (pretty much barren) calcareous mudstone with almost no lamination. Mineralization: 0.9% Zn & 0.4% Pb. »									
		« 251.50- 254.00 Barren siliceous mudstone displaying some bedding. Mineralization: 0.6% Zn & 0.2% Pb »									
		« 254.00- 255.10 Mineralized siliceous mudstone with a well developed lamination. Rich in sphalerite. Mineralization: 12% Zn & 4% Pb. »									
		« 255.10- 255.80 Limestone rich in pyrite and minor sphalerite and galena. Mineralization: 1.7% Zb & 0.7% Pb & 10% Fe. »									
		« 255.80- 256.00 Mineralized siliceous mudstone with well developed lamination. Mineralization: 14% Zn & 6% Pb. »									
		« 256.00- 256.60 Barren limestone rich in calcite veins. »									
		« 256.60- 260.20 Mainly mineralized and slightly calcareous to siliceous mudstone with moderately to well developed lamination. Mineralization: 3.5% Zn									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-210

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		& 0.8% Pb. Two bands (12mm thick and 20mm thick resp.) of high grade mineralization. » « 260.20- 262.00 Mainly limestone and very calcareous mudstone. Almost barren. Mineralization: 1.4% Zn & 0.4% Pb. » « 262.00- 262.30 High Grade. Whitish Grey Zn Pb Mudstone Facies. Massive sphalerite and galena. Mineralization: 20% Zn & 12% Pb. » « 262.30- 263.20 Slightly calcareous to siliceous mudstone with moderately developed lamination. Mineralization: 2.5% Zn & 1.3% Pb. » « 263.20- 265.30 High Grade. Whitish Grey Zn Pb Mudstone Facies. Massive mineralization: 22% Zn & 13% Pb. » « 265.30- 265.90 Siliceous mudstone with moderately to well developed lamination. Rich in sphalerite and low in galena. Mineralization: 15% Zn & 2% Pb. » « 265.90- 266.90 High Grade. Mainly Whitish Grey Zn Pb Mudstone Facies, mixed with minor barren mudstone. Mineralization: 18% Zn & 8% Pb. » « 266.90- 267.30 High Grade. Whitish Grey Zn Pb Mudstone Facies. Mineralization: 25% Zn & 13% Pb. » « 267.30- 268.30 Poorly mineralized calcareous mudstone with minor limestone. Mineralization: 1% Zn & 1% Pb. » « 268.30- 269.00 High Grade. Whitish Grey Zn Pb Mudstone Facies. Mineralization: 25% Zn & 15% Pb. » « 269.00- 269.10 Barren siliceous mudstone. » « 269.10- 269.90 High Grade. Whitish Grey Zn Pb Mudstone Facies. Mineralization 23% Zn & 12% Pb. »									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-210

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		« 269.90- 271.10 Siliceous mineralized mudstone with minor limestone. Mineralization: 3% Zn & 2% Pb. » « 271.10- 272.10 High Grade. Whitish Grey Zn Pb Mudstone Facies with minor barren siliceous mudstone. Mineralization: 14% Zn & 7% Pb. » « 272.10- 274.50 Barren calcareous mudstone with limestone. » « 274.50- 276.00 Barren siliceous mudstone. » « 276.00- 283.50 Mainly calcareous 'barren' (mineralization < 1%) mudstone. » « 283.50- 285.60 Flt »« Flt gg 25%»« Flt bx 25%»« Brco 50%» « 285.60- 289.30 Basal Light Grey Limestone »									
289.30	335.10	CCMS	634562	289.30	289.70	0.40	0.01	0.01	1.00	5.00	2.00
		CCMS – Calcareous Mudstone Massive, calcareous, carbonaceous, dark grey mudstone. Most of the member is massive, but rare poorly defined bedding and pyrite-calcite micro-concretions are present. Most diagnostic structures are feathery calcite beds (=thin calcite-cemented concretions, many of them contain pyrite cores) and calcite pseudo-beds (= fibrous calcite vein parallel to bedding). « lm ca 5.00-10.00mm », « nodules py -3.00% 2.00-20.00mm » « 289.30- 335.00 Classic CCMS. Throughout broken up. Locally poor recovery. Estimated 25% flt gg, 20% flt bx, 30% brco. » < @ 327.00 S0 defined by faint beds with minor pyrite S0 tca 29° > < @ 328.10 S0 defined by faint beds with minor pyrite S0 tca 25° >									



Selwyn Project
Diamond Drill Log

Hole Number:
XYC-210

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
335.10	335.10	EOH									

Diamond Drill Log

Comprehensive Report for Hole:

XYC-209

Hole No.: XYC-209	Depth: 583.50 m	Horizontal Length: 0.00 m	Project: 1710
Location Data:			
Property:	Selwyn Project	Claim Name:	X 4
Mining District:	Selywn Basin	Grant Number:	Y64529
Province/Territory:	Yukon		
UTM Co-Ordinates & Altitude of Drill Hole Collar:			
UTM Easting:	488628.46 m	True Azimuth:	15.0 °
UTM Northing:	6926781.99 m	Hole Angle:	-85.0 °
Elevation (m):	1703.26 m	NTS Name:	Placer Creek
		NTS Number:	105I06
Grid Co-Ordinates of Drill Hole Collar:			
Grid Easting (m):	0.00 m	Grid Name:	HP 06
Grid Northing (m):	0.00 m	Grid Type:	100m
Grid Azimuth:	75.0 °		
Dimond Drilling Contract:			
Drilled By:	NL-01	Date Drilling Start:	09/12/2010
		Date Finish:	09/30/2010
Diamond Drill Core:			
Logged By:	Kate Cameron / Matt Jodrey	Date Logging Start:	09/14/2010
		Date Finish:	10/03/2010
Legend for Core Logging Codes: PAX			
Core Size:	NQ/NQ3	Cemented:	Yes
Casing Depth:	50.30 m	Casing Pulled:	Yes
Water Depth:	0.00 m	Overburden Depth:	50.30 m
Level:	Section:	Drift:	

Selwyn Project

Diamond Drill Log

Survey Data for Hole

XYC-209

Hole Comments:

Sun, Sep 12 --- The 37 retrofit is complete, and we skidded the drill up to XY yesterday with the D7H. This morning we are setting up on setup # 24 (XYC-209). This was chosen because we want to take care of high drill sites before the snow hits, and because the 37 will fit more easily into setup #24 - a fairly small pad on steep slope.

=====

Mon, Sep 13 --- Put down casing yesterday and last night to 30 feet and started drilling, but they were still in overburden at that depth. Drilled to 20 meters, still not in bedrock. Will put down more casing once they pass through to bedrock.

=====

Tue, Sep 14 --- Issues continuing with casing and thick overburden. Casing is now down to 90 feet, and they have drilled through overburden beyond that to a total depth of 47.5 meters, where they believe they have now hit bedrock. They will put down more casing through the overburden today.

=====

Wed, Sep 15 --- NL-01 (XYC-209): Finally finished putting down casing to a depth of 50.2 meters. Drilling now at a depth of 57 meters in broken rock, likely BSSM.

=====

Thu, Sep 16 --- In Backside unit, in faulted zone. Total depth 112.0 m. No issues to report.

=====

Fri, Sep 17 --- Bit went yesterday afternoon; they are still in a fault zone within Backside. Slow going through difficult material.

=====

Sat, Sep 18 --- No issues to report. Still in Backside at 185 m, unit is competent. Missed Flexit test at 150 m, will have to get it at the end.

=====

Sun, Sep 19 --- Flexit for 150m was taken, paper found. No Flexit at 200 m because of badly faulted rock – they will take it as soon as they are in material that won't cave in. Drillers reported a block error for us to correct. Still in Flaggy.

=====

Mon, Sep 20 --- Large broken zone from 163-206 m. Contact between Flaggy and Upper Siliceous at approx. 235 m. No issues to report. Current depth 247 m.

=====

Tue, Sep 21 --- Drillers had problems with the bit, current depth 281 m. Unit is USMS.

=====

Wed, Sep 22 --- Correction to d_geol. Unit has been in Backside until today. Contact with FLMS at approx 290 m. Current depth 323 m in FLMS. No issues to report. Competent rock.

=====

Thu, Sep 23 --- Drilling continues at 368 m in USMS. Switching to split tube at 375 m. No issues to report.

=====

Fri, Sep 24 --- Waterline issues all night, no new core.

=====

Selwyn Project

Diamond Drill Log

Survey Data for Hole

XYC-209

Sat, Sep 25 --- Problems getting to and from the drill because of snowy road conditions. Cat is needed to tow the trucks. Current depth 401 m in Flaggy.

Sun, Sep 26 --- Still in Flaggy Mudstone at 437 m. No issues to report.

Mon, Sep 27 --- The hole was at 479m at morning shift change. During the last 24hrs 42m got drilled. It seems we are approaching the USMS, as the typical grey colour and bioturbations disappeared; no chert bands observed yet.

Tue, Sep 28 --- Total depth of the hole was at 518m at morning shift change. ACTM probably started around 512m as there was a 30cm long mineralized section running approximately 3% Zn. This could also be a short mineralized stretch in the USMS, as the core looks pretty barren and not typical USMS.

Wed, Sep 29 --- At a total depth of 536m and still in USMS. Yesterday's mineralization was local mineralization in USMS.

Thu, Sep 30 --- The total depth was 575m at morning shift change. They drilled 39m in the past 24hrs. The USMS-ACTM contact is at 544m. No impressive ACTM at all, low grade with locally (a 15cm piece) up to 12% combined. At approximately around 553m no more Zn or Pb was detected. From 555m to 566m the core is heavily veined with quartz. After that the core looks like CCMS. Matt will visit the drill this morning and then decide whether it gets shut down. If it gets shut down, then it will get moved to target #34.

<i>Depth</i>	<i>Dip</i>	<i>Azimuth</i>
0.00	-85.0	15.0
101.00	-84.6	9.3
152.00	-85.0	20.1
206.00	-83.8	14.7
254.00	-83.0	20.1
302.00	-83.2	33.3
350.00	-82.4	23.8
407.00	-82.4	33.5
452.00	-82.4	35.0
500.00	-81.5	34.3
550.00	-81.2	33.5
583.00	-81.0	34.9

Selwyn Project Diamond Drill Log

Hole Number:
XYC-209

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
0.00	50.30	OVBR									
50.30	280.90	BSSM									
BSSM – Backside Siliceous Mudstone											
Devonian Siliceous Mudstone – Upper Chert Formation											
Greyish black laminated chert and siliceous mudstone. Randomly-oriented to bedding-parallel bioturbation is common in the bottom of the unit. « lm chrt 75.00-95.00% », « btrb 0.10-2.00cm »,											
Flaggy-like black sections are abundant. Mostly dark grey carbonaceous siliceous mudstone with laminae. Elongate pyrite concretions with calcite halos on mm scale.											
« 50.30- 63.00 Surface breakage. »											
◁ @ 72.00 Lamination of dark grey cherty and black mudstone. S0 TCA 35° ▷											
◁ @ 84.30 Elongate pyrite blebs. S0 TCA 30° ▷											
« 92.10- 92.30 Minor Fault. FLT »« brco 30%»« flt bx 60%»« flt gg 10%»											
« 100.80- 102.70 FLT« brco 45%»« flt bx 50%»« flt gg 5%» »											
« 104.60- 113.00 Fault zone. FLT» « brco 30%»« flt bx 50%»« flt gg 20%»											
« 116.50- 119.30 FLT »« brco 20%»« flt bx 50%»« flt gg 30%»											
« 119.50- 132.50 FLT »« brco 5%»« flt bx 65%»« flt gg 30%»											
« 134.00- 135.00 FLT »« flt bx 90%»« flt gg 10%»											

Selwyn Project Diamond Drill Log

Hole Number:
XYC-209

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		« 136.00- 138.70 FLT »« brco 30%»« flt bx 70%» « 149.50- 150.00 FLT »« brco 20%»« flt gg 80%» « 151.00- 152.50 FLT »« flt bx 70%»« flt gg 30%» « 193.60- 195.00 FLT »« brco 5%»« flt bx 30%»« flt gg 65%» « 197.00- 206.00 Fault and some void. Drilling problems resulting in very little recovery and pieces turned in the drill. Fragments are polished and mechanically broken. Hard to tell the original state of the fault. FLT »« brco 30%»« flt bx 65%»« flt gg 5%»									
280.90	460.70	FLMD									
FLMD – Flaggy Mudstone Formation Dark grey mudstone in the upper portions of the unit grading into light grey mudstone to siltstone. Contains abundant wispy bioturbation which ranges from randomly-oriented at the top of the unit to bedding-parallel throughout the majority of the unit. Darker upper section has a strong fetid odour along broken surfaces. « btrb 0.10-2.00cm », « cg xtl crns ca 1.00-5.00% 5.00-150.00cm », « crns py 1.00-5.00% 0.10-0.50mm », ----- ----- Mudstones with "bioturbation" ranging in colour from light to dark grey, having limestone concretions as well as calcite and silica alteration. Frequent quartz-calc veins from a few mm up to a few cm wide. Intercalated dark gery and light grey sections. Pyrite blebs with calcite halos are common. ◁ @ 330.00 Undistorted dark laminae S0 TCA 30° ▷ ◁ @ 333.00 Bedding in laminae S0 TCA 20° ▷											

Selwyn Project Diamond Drill Log

Hole Number:
XYC-209

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
< @ 344.00 Bedding in laminae S0 TCA 10° > < @ 360.00 Bedding in laminae and dark layers. S0 TCA 60° > < @ 418.60 Bedding in laminae S0 TCA 50° > < @ 454.50 Carbonaceous beds S0 TCA 47° >											
460.70	537.40	USMS	633551	536.00	537.40	1.40	0.01	0.05	1.00	5.00	0.20
USMS – Upper Siliceous Mudstone Consists of interlaminated dark grey to black mudstone and light to medium grey chert. Regionally, a 1m thick graptolite zone occurs 15m below the top of the upper unit, this is usable as a horizon. The USMS is divided into 3 units. The Lower Unit contains abundant limestone concretions and Galena and sphalerite micro-concretions occur locally near the base of this unit. « gra , lm chrt -20.00% », « cg xtl sph crns ca 5.00-20.00cm », « bed chrt 10.00-15.00% », ----- ----- Typical, competent, abundant chert-carbonate banding. Rare carbonate concretions. « 460.70- 477.30 Dark grey siliceous mdst without chert/carbonate banding or laminations » < @ 483.50 Defined by the general orientation of local chert banding S0 tca 34° > > « 484.80- 484.90 FLT »« flt gg 50%»« flt bx 50%» « 504.40- 504.60 FLT »« flt gg 50%»« flt bx 50%» « 505.30- 505.60 FLT »« flt gg 20%»« flt bx 30%»« brco 50%»											

Selwyn Project Diamond Drill Log

Hole Number:
XYC-209

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
< @ 512.40 Defined by a pyrite rich bed S0 tca 30° > « 512.40- 513.00 Faint laminations with trace Zn mineralization » « 514.40- 514.50 FLT »« flt gg 50%»« flt bx 50%» « 527.20- 527.30 Minor FLT »« flt gg 50%»« flt bx 50%» « 529.20- 530.00 Package of small faults FLT » < @ 530.30 Defined by parallel chert bands S0 tca 26° >											
537.40	555.60	ACTM	633552	537.40	538.00	0.60	1.59	3.74	3.00	110.00	0.43
ACTM – Active Member The ACTM consists of a repetitive, possibly rhythmic, sequence of intercalated carbonaceous mudstone, cherty mudstone, chert and limestone and locally contains economically significant Zn and Pb sulphides (see bold marked facies), mainly in its sections with well developed lamination. Because of its heterogeneity, the member is distinctive and easily identified. ===== The ACTM has 8 different facies: =====			633553	538.00	538.40	0.40	0.13	0.49	1.00	20.00	0.27
			633554	538.40	539.00	0.60	0.16	1.08	1.00	30.00	0.15
			633555	539.00	540.00	1.00	1.02	4.09	3.00	120.00	0.25
			633556	540.00	541.00	1.00	1.15	4.96	3.00	150.00	0.23
			633557	541.00	541.60	0.60	0.10	0.36	1.00	10.00	0.28
			633558	541.60	542.10	0.50	3.08	8.76	7.00	270.00	0.35
			633559	542.10	542.60	0.50	0.58	2.44	1.00	80.00	0.24
			633560	542.60	543.20	0.60	0.57	3.48	3.00	110.00	0.16
			633561	542.60	543.20	0.60	0.68	3.34	1.00	100.00	0.20
			633562	543.20	543.90	0.70	7.62	10.45	9.00	330.00	0.73
			633563	543.90	544.60	0.70	2.60	6.33	4.00	220.00	0.41
			633564	544.60	545.40	0.80	4.18	11.32	5.00	400.00	0.37

Selwyn Project Diamond Drill Log

Hole Number:
XYC-209

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
- GREY CHERT FACIES: Consists of laminated medium light grey to medium dark grey chert. Mineralization: 95-99% quartz and up to 5% secondary calcite. - WHITISH GREY ZN-PB MUDSTONE FACIES: Is a laminated cherty rock containing up to 70% sulphides. Mineralization: quartz, sphalerite and galena are the major minerals with only minor amounts of pyrite and locally calcite. Sedimentary diagenetic structures are common and well displayed in the facies, such as: lamination, pseudo-beds, calcite nodules & limestone nodules and abundant water escape structures. Most obvious structure in facies is cross-cutting veins containing massive sphalerite and galena with minor pyrite. They range in width from 0.5 to 10mm. - THIN BEDDED CHERTY MUDSTONE FACIES: Consists of rhythmic intercalated laminae of chert, carbonaceous mudstone and minor micrite. This facies contains significant amounts of Zn and Pb sulphides. - CHERTY MUDSTONE FACIES: Consists of a greyish black monotonous siliceous, carbonaceous mudstone. It is most typically found overlying the thin bedded calcareous mudstone facies. - THIN BEDDED CALCAREOUS MUDSTONE FACIES: Consists of laminated carbonaceous mudstone containing 20-40% calcite, 40-55% quartz and 10-20% muscovite. Sulphides occur in laminae. In the XY area it is usually the lowest facies in the section to contain laminated sulphides. - CALCAREOUS MUDSTONE FACIES: Consists of grey to greyish black monotonous, calcareous siliceous carbonaceous mudstone. There are no feathery calcite beds or pyrite-calcite blebs in the facies, making it easily distinguishable from the CCMS. - GRADED LIMESTONE FACIES: Is a laminated argillaceous limestone with intercalated carbonaceous limestone laminae. The main rock type in the facies is laminated limestone with laminae up to 0.1-7mm thick.			633565	545.40	545.90	0.50	2.15	7.02	3.00	200.00	0.31
			633566	545.90	546.30	0.40	0.10	0.61	1.00	20.00	0.16
			633567	546.30	547.00	0.70	1.64	1.98	1.00	60.00	0.83
			633568	547.00	547.90	0.90	0.21	0.42	1.00	10.00	0.50
			633569	547.90	548.60	0.70	0.53	0.48	2.00	10.00	1.10
			633570	548.60	548.60	0.00	0.01	0.01	1.00	5.00	2.00
			633571	548.60	549.40	0.80	0.06	0.29	1.00	5.00	0.21
			633572	549.40	550.60	1.20	0.07	0.72	1.00	20.00	0.10
			633573	550.60	551.80	1.20	0.28	0.82	3.00	20.00	0.34
			633574	551.80	552.10	0.30	0.07	0.23	1.00	5.00	0.30
			633575	552.10	553.00	0.90	0.19	0.64	1.00	20.00	0.30
			633576	553.00	553.70	0.70	1.41	0.81	6.00	20.00	1.74
			633577	553.70	554.30	0.60	0.18	0.59	1.00	20.00	0.31
			633578	554.30	555.00	0.70	0.14	0.51	1.00	10.00	0.27
			633579	555.00	555.60	0.60	0.15	2.94	1.00	100.00	0.05

Selwyn Project Diamond Drill Log

Hole Number:
XYC-209

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		- <i>LIGHT GREY BASAL LIMESTONE FACIES - LGLS: Consists of laminated argillaceous limestone. In the Anniv area it marks the end of the ACTM. It's not always present in the stratigraphy.</i> - <i>BASAL FACIES: This is a highly contorted and locally foliated carbonaceous mudstone. Unlike the other facies it is not repeated higher in the member. It appears locally to contain the slip zone of a major slump. The facies has only been observed in the YX area. It is 0.1-2m thick. The facies consists of massive carbonaceous siliceous mudstone with lenses and laminae of contorted, slightly carbonaceous chert.</i> <i>Narrow, low-grade intersection. Includes abundant limestone. Relatively very competent. Generally unlaminated.</i> « 537.40- 538.40 Weakly laminated lt grey lmst with minor, weakly laminated siliceous mdst. » « 538.40- 539.00 Siliceous mdst (unlaminated) breccia with angular lmst clast. » « 539.00- 541.00 Breccia of primarily lmst fragments, lesser weakly laminated (sph) siliceous mdst. » « 541.00- 542.10 Brecciated, med grey calc mdst. Angular lmst clasts. Interbedded dark grey weakly laminated Si_mdst with minor ga stringers. » « 542.10- 543.20 Breccia, dominatly lt grey lmst clast with minor dk grey mdst matrix. Unlaminated, no visible mineralization. » « 543.20- 543.90 Breccia, dark grey weakly calcareous mdst with minor lmst. Weak/moderate visible mineralization. Ga stringers. » « 543.90- 545.40 Breccia, dark grey mdst and light grey lmst. Some lt									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-209

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		grey mdst clasts. Very little visible mineralization. » « 545.40- 545.90 Breccia, dark grey unlaminated mdst matrix and clast of laminated mineralized light grey mdst. » « 545.90- 546.30 Breccia, siliceous mdst matrix with minor light grey lmst clast. Unlaminated. No visible mineralization. » « 546.30- 547.00 Medium grey lmst clast with minor siliceous mdst matrix. No visible mineralization » « 547.00- 548.60 Primarily light grey sheared brecciated lmst with minor unlaminated calcareous mdst. No visible mineralization. Basal lmst appearance. » « 548.60- 550.60 Medium grey lmst with a sheared quality. No visible mineralization. » « 550.60- 555.00 Non to weakly calc mdst with abundant micro calcite veins and abundant small (<2cm) lmst clast. Unlaminated, no visible mineralization. » « 555.00- 555.60 As above with more mineralization »									
555.60	583.50	CCMS	633580	555.60	555.60	0.00	6.12	6.68	71.00	180.00	0.92
		CCMS – Calcareous Mudstone	633581	555.60	556.60	1.00	0.01	0.03	1.00	5.00	0.33
			633582	556.60	557.20	0.60	0.01	0.07	1.00	5.00	0.14
		Massive, calcareous, carbonaceous, dark grey mudstone. Most of the member is massive, but rare poorly defined bedding and pyrite-calcite micro-concretions are present. Most diagnostic structures are feathery calcite beds (=thin calcite-cemented concretions, many of them contain pyrite cores) and calcite pseudo-beds (= fibrous calcite vein parallel to bedding). « lm ca 5.00-10.00mm », « nodules py -3.00% 2.00-20.00mm », Generally typical with the exception of the top veined range (see below)									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-209

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		« 555.60- 566.00 Heavily veined (calcite) throughout range; ~30% vein material in core. Very broken with gouge and slicken slide surfaces on fractures faces » < @ 575.20 Defined by ca/py rich beds S0 tca 19° >									
583.50	583.50	EOH									

Selwyn Project

Diamond Drill Log

Comprehensive Report for Hole:

XYC-208

Hole No.: XYC-208	Depth: 548.90 m	Horizontal Length: 0.00 m	Project: 1710
Location Data:			
Property:	Selwyn Project	Claim Name:	X 4
Mining District:	Selywn Basin	Grant Number:	Y 64529
Province/Territory:	Yukon		
UTM Co-Ordinates & Altitude of Drill Hole Collar:			
UTM Easting:	488828.00 m	True Azimuth:	200.0 °
UTM Northing:	6926764.00 m	Hole Angle:	-86.5 °
Elevation (m):	1760.00 m	NTS Name:	Placer Creek
		NTS Number:	105I06
Grid Co-Ordinates of Drill Hole Collar:			
Grid Easting (m):	0.00 m	Grid Name:	HP 06
Grid Northing (m):	0.00 m	Grid Type:	100m
Grid Azimuth:	260.0 °		
Dimond Drilling Contract:			
Drilled By:	NL-03	Date Drilling Start:	09/10/2010
		Date Finish:	09/19/2010
Diamond Drill Core:			
Logged By:	Gabe Xue / Kate Cameron	Date Logging Start:	09/12/2010
		Date Finish:	09/27/2010
Legend for Core Logging Codes: PAX			
Core Size:	NQ3	Cemented:	Yes
Casing Depth:	18.30 m	Casing Pulled:	Yes
Water Depth:	0.00 m	Overburden Depth:	18.30 m
Level:			
Section:		Drift:	

Selwyn Project

Diamond Drill Log

Survey Data for Hole

XYC-208

Hole Comments:

Sat, Sep 11 --- Moved rig to setup # 16 yesterday - the highest setup on the hill. Night shift put down 60 feet of casing and drilled through very broken-up, weathered, BSSM to a depth of 35 meters.

=====

Sun, Sep 12 --- In fairly broken up BSSM after drilling 69 meters over the past day. Graded bedding indicates that we are likely quite high in the stratigraphy. Drilling is going well.

=====

Mon, Sep 13 --- Drilling through BSSM (or what might technically be Iron Creek, above BSSM) at 192 meters. The core is very broken and contains several faults from 176 meters to current depth. No mechanical problems to report.

=====

Tue, Sep 14 --- Yesterday and last night they drilled through a massive fault in BSSM. The core is primarily a mix of broken core, fault breccia, and fault gouge from 208 to 247 meters. They are now at 249 meters, and they seem to have emerged from the fault.

=====

Wed, Sep 15 --- NL-03 (XYC-208): In competent FLMD at 353 meters; no mechanical problems; drilling going well.

=====

Thu, Sep 16 --- Flaggy mudstone ends at approx. 1223 ft/ 373m. Into upper siliceous, which is faulted here. Pump quit near AM shift change, running again now.

=====

Fri, Sep 17 --- Bit went yesterday afternoon. Waterline froze last night and gave them issues all night. No core new core from night shift.

=====

Sat, Sep 18 --- Still slow going in faulted zone. One competent stretch from 471 m to 493 m looks like Active Member, then back into heavily faulted Upper Siliceous-like material.

=====

Sun, Sep 19 --- Slow going through multiple faulted sections. Two sections of ACTM, ending at approx. 1736. Then into CCMS. Hole shutting down. Move to setup #8 today.

<i>Depth</i>	<i>Dip</i>	<i>Azimuth</i>
0.00	-86.5	200.0
48.20	-86.0	192.0
93.90	-85.9	178.7
139.60	-85.6	192.6
183.20	-85.0	189.7
231.00	-84.0	186.0
276.10	-83.3	188.1
322.50	-82.8	189.1
368.20	-82.3	184.0
413.90	-81.9	184.9
460.90	-81.2	193.7
506.60	-80.4	189.1

Selwyn Project

Diamond Drill Log

Survey Data for Hole

XYC-208

Selwyn Chihong Mining Ltd.#700-509 Richards Street
Vancouver, British Columbia
Canada V6B 2Z6

548.90

-79.9

193.8

Selwyn Project

Diamond Drill Log

Hole Number:

XYC-208

Selwyn Chihong Mining Ltd.
 #700-509 Richards Street
 Vancouver, British Columbia
 Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
0.00	18.30	OVBR									
18.30	212.40	FECR									
FECR – Iron Creek Formation											
Mudstones to fine grained sandstones showing ubiquitous graded beds. The formation is subdivided into 6 informal units. The most significant unit regionally is the Selwyn Mountains barite horizon.											
« crns ba 2.00-10.00mm »,											
« 18.30- 44.50 Fairly broken core: Dark-grey si_mst with orange & greenish coating on CLVG; core is broken into shalley pieces; quite massive, no apparents beds. »											
« 44.50- 68.90 Dark-grey si_mst, quite massive; no apparent beds or bands visible; stylolitic fractures are seen locally; interlayered with following graded si_mst »« Underlaying in gradational contact, medium-dark grey si_mst with graded beds; elongated py concretions are laminated and paralleling to the beds »											
< @ 75.90 On graded beds S0 tca 71° >											
« 78.00- 80.50 Qtz+-ca vein containing grey si_mst clasts »											
« 81.70- 82.90 Qtz+-ca vein »											
« 82.90- 85.30 Broken qtz+-ca vein & mst clasts FLT »« flt gg 20%»« flt bx 40%»« brkn core 40%»											
« 91.40- 94.20 Qtz+-ca vein containing grey si_mst clasts »											
< @ 98.80 On graded beds S0 tca 59° >											
< @ 112.60 On graded beds S0 tca 71° >											
< @ 144.50 On graded beds S0 tca 73° >											
< @ 174.40 On graded beds S0 tca 70° >											
« 176.80- 180.70 Broken black mst & ca vein FLT »« flt gg 15%»« flt bx											

Selwyn Project Diamond Drill Log

Hole Number:
XYC-208

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		20%»« brkn core 65%» « 182.90- 183.50 Well developed veining » « 192.50- 200.30 FLT »« flt gg 20%»« flt bx 40%»« brkn core 40%» « 205.70- 206.30 Clast supported breccia with thin laminated mst (yellowish greys) » « 210.30- 211.50 Siltstone »									
212.40	253.60	BSSM									
		BSSM – Backside Siliceous Mudstone Devonian Siliceous Mudstone – Upper Chert Formation Greyish black laminated chert and siliceous mudstone. Randomly-oriented to bedding-parallel bioturbation is common in the bottom of the unit. « lm chrt 75.00-95.00% », « btrb 0.10-2.00cm », Black si_mst with squiggly bands « 218.20- 253.60 FLT »« flt gg 30%»« flt bx 40%»« brkn mst & qtz veins & lmst nodules 30%»									
253.60	369.50	FLMD									
		FLMD – Flaggy Mudstone Formation Dark grey mudstone in the upper portions of the unit grading into light grey mudstone to siltstone. Contains abundant wispy bioturbation which ranges from randomly-oriented at the top of the unit to bedding-parallel throughout the majority of the unit. Darker upper section has a strong fetid odour along									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-208

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
broken surfaces. « btrb 0.10-2.00cm », « cg xtl crns ca 1.00-5.00% 5.00-150.00cm », « crns py 1.00-5.00% 0.10-0.50mm », Light-medium grey FLMD; Bioturbated beds vary from 0-60 degrees tca. ‹ @ 297.20 On black bands with faint laminated py S0 tca 33° › ‹ @ 334.10 On the silt stone bed in 3cm width S0 tca 57° › « 359.10- 365.20 Heavily fractured zone » « 369.00- 376.40 FLT »« brkn core 20%»« flt bx 70%»« flt gg 10%»											
369.50	483.50	USMS	632801	481.30	482.10	0.80	0.22	0.34	1.00	10.00	0.65
USMS – Upper Siliceous Mudstone			632802	482.10	483.50	1.40	1.85	8.96	4.00	300.00	0.21
Consists of interlaminated dark grey to black mudstone and light to medium grey chert. Regionally, a 1m thick graptolite zone occurs 15m below the top of the upper unit, this is usable as a horizon. The USMS is divided into 3 units. The Lower Unit contains abundant limestone concretions and Galena and sphalerite micro-concretions occur locally near the base of this unit. « gra , lm chrt -20.00% », « cg xtl sph crns ca 5.00-20.00cm », « bed chrt 10.00-15.00% », ----- ----- « 381.00- 387.50 Fault with slick n slides. FLT »« brco 5%»« flt bx 50%»« flt gg 45%» ‹ @ 397.00 Bedding in laminae, foliation and cherty bands. S0 TCA 30-40° › « 403.80- 404.30 FLT »« brco 10%»« flt bx 80%»« flt gg 10%» « 449.00- 450.10 Fault with slick n slides FLT »« brco 60%»« flt bx 30%»« flt gg 10%» « 458.50- 459.40 Heavily fractured zone. »											

Selwyn Project Diamond Drill Log

Hole Number:
XYC-208

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
« 462.20- 484.70 Fault zone. Heavily fractured with several small zones of breccia and gouge. Some slick n slided surfcaes. FLT »											
483.50	527.10	ACTM	632803	483.50	483.80	0.30	0.29	0.06	1.00	5.00	4.83
ACTM – Active Member			632804	483.80	484.20	0.40	0.53	1.89	1.00	70.00	0.28
The ACTM consists of a repetitive, possibly rhythmic, sequence of intercalated carbonaceous mudstone, cherty mudstone, chert and limestone and locally contains economically significant Zn and Pb sulphides (see bold marked facies), mainly in its sections with well developed lamination. Because of its heterogeneity, the member is distinctive and easily identified. ===== The ACTM has 8 different facies: ===== - GREY CHERT FACIES: Consists of laminated medium light grey to medium dark grey chert. Mineralization: 95-99% quartz and up to 5% secondary calcite. - WHITISH GREY ZN-PB MUDSTONE FACIES: Is a laminated cherty rock containing up to 70% sulphides. Mineralization: quartz, sphalerite and galena are the major minerals with only minor amounts of pyrite and locally calcite. Sedimentary diagenetic structures are common and well displayed in the facies, such as: lamination, pseudo-beds, calcite nodules & limestone nodules and abundant water escape structures. Most obvious structure in facies is cross-cutting veins containing massive sphalerite and galena with minor pyrite. They range in width from 0.5 to 10mm. - THIN BEDDED CHERTY MUDSTONE FACIES: Consists of rhythmic intercalated laminae of chert, carbonaceous mudstone and minor micrite. This facies contains significant amounts of Zn and Pb sulphides. - CHERTY MUDSTONE FACIES: Consists of a greyish black monotonous siliceous,			632805	484.20	484.70	0.50	1.35	3.16	1.00	90.00	0.43
			632806	484.70	486.30	1.60	0.30	0.39	1.00	10.00	0.77
			632807	486.30	486.60	0.30	0.13	1.16	1.00	40.00	0.11
			632808	486.60	488.30	1.70	0.14	0.32	1.00	10.00	0.44
			632809	488.30	489.60	1.30	1.49	10.89	3.00	300.00	0.14
			632810	489.60	491.50	1.90	0.27	1.04	1.00	30.00	0.26
			632811	489.60	491.50	1.90	0.60	1.42	1.00	40.00	0.42
			632812	491.50	492.10	0.60	0.91	3.20	1.00	90.00	0.28
			632813	492.10	493.40	1.30	1.18	2.46	1.00	90.00	0.48
			632814	493.40	495.00	1.60	1.22	3.65	1.00	100.00	0.33
			632815	495.00	497.20	2.20	1.55	7.84	1.00	230.00	0.20
			632816	497.20	498.60	1.40	1.36	4.82	1.00	130.00	0.28
			632817	498.60	500.40	1.80	0.83	0.21	1.00	5.00	3.95
			632818	500.40	501.60	1.20	0.97	3.63	2.00	110.00	0.27
			632819	501.60	502.50	0.90	18.28	18.29	11.00	1080.00	1.00
			632820	502.50	502.50	0.00	0.01	0.01	1.00	5.00	2.00
			632821	502.50	503.50	1.00	18.59	23.18	12.00	1230.00	0.80
			632822	503.50	504.00	0.50	18.05	25.04	13.00	1300.00	0.72
			632823	504.00	505.00	1.00	18.07	10.08	13.00	630.00	1.79
			632824	505.00	506.40	1.40	18.52	13.99	16.00	880.00	1.32
			632825	506.40	507.40	1.00	9.90	9.72	9.00	490.00	1.02
			632826	507.40	508.40	1.00	0.10	0.14	1.00	5.00	0.71
			632827	508.40	509.20	0.80	0.50	0.03	1.00	5.00	16.67
			632828	509.20	510.00	0.80	0.13	0.71	1.00	20.00	0.18
			632829	510.00	511.50	1.50	0.08	1.79	3.00	80.00	0.04
			632830	511.50	511.50	0.00	5.74	6.51	67.00	180.00	0.88
			632831	511.50	512.20	0.70	0.32	0.27	3.00	10.00	1.19
			632832	512.20	513.10	0.90	0.07	0.11	1.00	5.00	0.64

Selwyn Project Diamond Drill Log

Hole Number:
XYC-208

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
carbonaceous mudstone. It is most typically found overlying the thin bedded calcareous mudstone facies. - THIN BEDDED CALCAREOUS MUDSTONE FACIES: Consists of laminated carbonaceous mudstone containing 20-40% calcite, 40-55% quartz and 10-20% muscovite. Sulphides occur in laminae. In the XY area it is usually the lowest facies in the section to contain laminated sulphides. - CALCAREOUS MUDSTONE FACIES: Consists of grey to greyish black monotonous, calcareous siliceous carbonaceous mudstone. There are no feathery calcite beds or pyrite-calcite blebs in the facies, making it easily distinguishable from the CCMS. - GRADED LIMESTONE FACIES: Is a laminated argillaceous limestone with intercalated carbonaceous limestone laminae. The main rock type in the facies is laminated limestone with laminae up to 0.1-7mm thick. - LIGHT GREY BASAL LIMESTONE FACIES - LGLS: Consists of laminated argillaceous limestone. In the Anniv area it marks the end of the ACTM. It's not always present in the stratigraphy. - BASAL FACIES: This is a highly contorted and locally foliated carbonaceous mudstone. Unlike the other facies it is not repeated higher in the member. It appears locally to contain the slip zone of a major slump. The facies has only been observed in the YX area. It is 0.1-2m thick. The facies consists of massive carbonaceous siliceous mudstone with lenses and laminae of contorted, slightly carbonaceous chert. ----- « 483.50- 484.00 Reactivated calcite vein, originally containing pyrite, is now py-calc breccia. »			632833	513.10	513.80	0.70	0.06	0.17	2.00	5.00	0.35
			632834	513.80	515.70	1.90	0.48	0.72	5.00	20.00	0.67
			632835	515.70	516.70	1.00	0.02	0.14	1.00	5.00	0.14
			632836	516.70	517.80	1.10	0.06	0.34	1.00	10.00	0.18
			632837	517.80	518.80	1.00	0.03	0.47	1.00	10.00	0.06
			632838	518.80	520.30	1.50	0.09	0.31	3.00	5.00	0.29
			632839	520.30	521.80	1.50	0.21	0.11	3.00	5.00	1.91
			632840	521.80	523.30	1.50	0.15	2.20	5.00	70.00	0.07
			632841	521.80	523.30	1.50	0.09	1.45	4.00	50.00	0.06
			632842	523.30	523.60	0.30	0.08	5.48	7.00	180.00	0.01
			632843	523.60	525.20	1.60	0.08	0.24	1.00	5.00	0.33
			632844	525.20	526.70	1.50	0.01	0.01	1.00	5.00	2.00

Selwyn Project

Diamond Drill Log

Hole Number:
XYC-208

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		« 484.00- 484.20 Limestone. Coarse grained, medium grey, monotonous. Trace mineralization. »									
		« 484.20- 484.70 Black mudstone. Siliceous, carbonaceous. Sphalerite mineralization. »									
		« 484.20- 484.30 FLT »« flt bx 40%»« flt gg 60%»									
		« 484.70- 486.30 Medium to coarse grained limestone, monotonous. Galena mineralization. »									
		« 486.30- 486.60 Dark grey carbonaceous mudstone with sphalerite in laminae. »									
		« 486.60- 488.30 Limestone. Faint to moderate lamination. No visible mineralization. »									
		« 488.30- 489.60 Black mudstone with fine laminae containing sphalerite. Laminae are well folded. Sphalerite also occurs as reddish-brown crystal aggregates in calcite vein. Galena also visible. Good grade mineralization. »									
		« 489.60- 493.40 Coarse limestone with intense calcite stringers and veining. Trace mineralization. Last 50 cm is badly broken up and more intensely spider-veined with calcite. »									
		« 492.40- 498.50 FLT »« brco 5%»« flt bx 85%»« flt gg 10%»									
		« 493.40- 498.60 Black mudstone, very well broken up. Larger fragments show intense sphalerite laminae. »									
		« 498.60- 500.40 Limestone. Coarse, weakly graded, no mineralization visible. »									
		« 500.40- 501.60 Black laminated mudstone, well broken up. Good sphalerite and galena mineralization. Whole unit is a fault zone. »« FLT »«									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-208

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		flt bx 95%»« flt gg 5%» « 501.60- 504.00 Light grey laminated mudstone with calcareous, sphalerite and galena laminae. Ga and Sph also occur coarsely crystalline. High grade mineralization. »« SPH 20-25% »« GA 10-15%» « 504.00- 509.20 Limestone. Medium grey. Carbonaceous, moderately laminated. Galena mineralization. Graded 0.5 to 2 cm beds of alternating dark and light grey limestone. Perfectly planar, very thin calcite veins. Pyrite and calcite blebs and irregular veins up to 10 cm. Good grade mineralization by visual estimate. »« GA 10%»« SPH 5%» « 509.20- 510.00 Siliceous black mudstone with wormy calcite veins 0.5 cm wide and limestone concretions 5 cm wide. Trace mineralization. » « 510.00- 512.20 Carbonaceous, highly calcareous mudstone with faint but dense calcite/limestone laminae and sphalerite laminae. Multiple wormy calcite veins in bottom 40 cm. » « 512.20- 513.10 Coarse, finely laminated limestone. No veining, or distortion of beds whatsoever. Laminae contain darker carbonaceous material. No visual mineralization. » « 513.10- 513.80 Limestone laminated with mudstone. Calcite veins are abundant, and often have associated pyrite. Changes from light to medium, to dark grey depending on density of dark laminae. Trace mineralization? » « 513.80- 518.80 Fine grained limestone. Medium grey with faint, fine lamination. Disseminated pyrite throughout. Trace mineralization. » « 518.80- 523.60 Calcareous mudstone, medium to dark grey, without bedding or lamination. Frequent pyrite-calcite stringers and veins, which are folded in some sections. » « 523.60- 525.20 Siliceous, very dark grey to black mudstone. Wormy									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-208

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		calcite veins, and disseminated pyrite. » « 525.20- 527.80 Basal limestone. Light grey limestone with moderate lamination and planar calcite stringers. Some thicker calcite veins are wormy. No visual mineralization. Last 40 cm of section are medium grey, slightly carbonaceous limestone with some blueish gypsum infilling fractures.» « @ 527.70 5 cm of flt bx and flt gg associated with a zone originally containing increased calcite and gypsum veining. »									
			632845	526.70	527.40	0.70	0.01	0.01	1.00	5.00	2.00
527.10	548.90	CCMS	632846	527.40	527.80	0.40	0.02	0.01	1.00	5.00	4.00
		CCMS – Calcareous Mudstone	632847	527.80	529.30	1.50	0.03	0.05	1.00	5.00	0.60
			632848	529.30	530.80	1.50	0.03	0.01	1.00	5.00	6.00
		Massive, calcareous, carbonaceous, dark grey mudstone. Most of the member is massive, but rare poorly defined bedding and pyrite-calcite micro-concretions are present. Most diagnostic structures are feathery calcite beds (=thin calcite-cemented concretions, many of them contain pyrite cores) and calcite pseudo-beds (= fibrous calcite vein parallel to bedding).	632849	530.80	530.80	0.00	1.45	3.02	18.00	180.00	0.48
			632850	530.80	530.80	0.00	0.01	0.01	1.00	5.00	2.00
		« lm ca 5.00-10.00mm », « nodules py -3.00% 2.00-20.00mm », ----- ----- Classic CCMS. Black, siliceous, monotonous. Very thin planar stringers of pure calcite are widely spaced. Occasional disseminated bands of pyrite with calcite filled stylolites, widely spaced. Whispy calcite bits. Minor limestone concretions with disseminated pyrite. « 543.50- 544.80 FLT »« flt bx 70%»« flt gg 30%» « @ 548.90 EOH »									
548.90	548.90	EOH									

Selwyn Project

Diamond Drill Log

Comprehensive Report for Hole:

XYC-207

Hole No.: XYC-207	Depth: 470.90 m	Horizontal Length: 0.00 m	Project: 1710
Location Data:			
Property:	Selwyn Project	Claim Name:	X 2
Mining District:	Selwyn Basin	Grant Number:	Y 64527
Province/Territory:	Yukon		
UTM Co-Ordinates & Altitude of Drill Hole Collar:			
UTM Easting:	488416.00 m	True Azimuth:	335.0 °
UTM Northing:	6926726.00 m	Hole Angle:	-75.0 °
Elevation (m):	1585.00 m	NTS Name:	Placer Creek
		NTS Number:	105L06
Grid Co-Ordinates of Drill Hole Collar:			
Grid Easting (m):	0.00 m	Grid Name:	HP 06
Grid Northing (m):	0.00 m	Grid Type:	100m
Grid Azimuth:	35.0 °		
Dimond Drilling Contract:			
Drilled By:	NL-02	Date Drilling Start:	09/08/2010
		Date Finish:	09/16/2010
Diamond Drill Core:			
Logged By:	Graham Leroux / Gabe Xue	Date Logging Start:	09/12/2010
		Date Finish:	09/27/2010
Legend for Core Logging Codes: PAX			
Core Size:	NQ3	Cemented:	Yes
Casing Depth:	12.90 m	Casing Pulled:	Yes
Water Depth:	0.00 m	Overburden Depth:	12.90 m
Level:			
Section:		Drift:	

Selwyn Project

Diamond Drill Log

Survey Data for Hole

XYC-207

Hole Comments:

Thu, Sep 09 --- Shut down XYC-205 yesterday in footwall and oriented drill for XYC-207 (setup #32) on same pad. Day shift and night shift put down a total of 12.2 meters of casing, and have now drilled to a depth of 41.3 meters. Rock is BSSM, and drilling is slow due to blocky core.

=====

Fri, Sep 10 --- Drilling going well in BSSM; at 101 meters with 60 meters drilled over the past day. First bioturbations are observed at 56 meters.

=====

Sat, Sep 11 --- Good drilling at 152.3 meters, with light grey bioturbated mudstone since 123 meters (likely the BSSM-FLMD contact). Last night the drill had a problem with a gear in the hydraulic pump of the hub, but it was quickly replaced and drilling continued throughout the night.

=====

Sun, Sep 12 --- In competent FLMD at 216 meters, with no mechanical problems to report.

=====

Mon, Sep 13 --- Drilling going well through competent USMS. The FLMD - USMS contact is at approximately 259 meters.

=====

Tue, Sep 14 --- Drilling through competent USMS at 336.5 meters. Late last night the driller slammed the swivel into the frame, bending it and effectively ending their shift early. It will be replaced this morning and drilling will continue.

=====

Wed, Sep 15 --- NL-02 (XYC-207): In USMS at a depth of 385 meters, after drilling 48 meters over the past two shifts. No sign of mineralization yet. Core is somewhat broken-up. No mechanical problems to report.

=====

Thu, Sep 16 --- Upper contact with active member at about 390 m. Fault zone above it. We have not encountered light grey limestone, but we are in a CCMS-like unit. Possible contact at approx. 400 m – but need to log it to be sure. No issues at the drill.

=====

Fri, Sep 17 --- EOH at 470.9 m. Shut down at midnight. Basal limestone marks the base of ACTM at ~435 m, followed by CCMS to EOH. Moving drill to XYC-209 today.

<i>Depth</i>	<i>Dip</i>	<i>Azimuth</i>
0.00	-75.0	335.0
50.00	-75.7	336.1
100.00	-75.4	335.6
155.30	-75.0	345.2
202.00	-75.8	343.2
250.00	-75.8	349.9
303.50	-77.2	343.1
351.50	-76.9	345.6
402.00	-76.4	352.6
450.00	-76.1	350.3

Selwyn Project Diamond Drill Log

Hole Number:
XYC-207

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
0.00	12.90	OVBR									
12.90	61.80	BSSM									
BSSM – Backside Siliceous Mudstone											
Devonian Siliceous Mudstone – Upper Chert Formation											
Greyish black laminated chert and siliceous mudstone. Randomly-oriented to bedding-parallel bioturbation is common in the bottom of the unit. « lm chrt 75.00-95.00% », « btrb 0.10-2.00cm »,											
« 12.90- 61.80 Dark grey si-mudstone with medium grey limestone nodules; locally black stretches (bioturbations?) are seen; v.f.g py+qt defined faint beds are visible; stylolitic lines occur in limestone nodules and mudstone.»											
< @ 20.50 S0 defined by faint py beds 47° tca >											
« 22.90- 29.40 Flt »« Flt gg 5%»« Flt bx 15%»« Brco 80%»											
< @ 29.30 convoluted py beds and wormy burrows? >											
« 33.30- 34.50 Flt »« Flt gg 5%»« Flt bx 10%»« Brco 85%»											
« 38.20- 40.50 broken mst Flt »« Flt gg 10%»« Flt bx 40%»« Brco 50%»											
< @ 38.20 bioturbated beds? ichnofossils >											
« 54.30- 55.90 broken mst Flt »« Flt gg 5%»« Flt bx 10%»« Brco 85%»											
« 57.10- 59.40 broken mst Flt »« Flt gg 10%»« Flt bx 40%»« Brco 50%»											
61.80	84.60	FLMD									
FLMD – Flaggy Mudstone Formation											
Dark grey mudstone in the upper portions of the unit grading into light grey											

Selwyn Project Diamond Drill Log

Hole Number:
XYC-207

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		mudstone to siltstone. Contains abundant wispy bioturbation which ranges from randomly-oriented at the top of the unit to bedding-parallel throughout the majority of the unit. Darker upper section has a strong fetid odour along broken surfaces. « btrb 0.10-2.00cm », « cg xtl crns ca 1.00-5.00% 5.00-150.00cm », « crns py 1.00-5.00% 0.10-0.50mm », « 73.10- 74.70 Flt »« Flt gg 5%»« Flt bx 55%»« Brco 40%» < @ 76.80 S0 on blk bioturbations S0 52° tca > « 78.60- 83.90 grey limestone nodules with graded beds and thin calcite infilled stylolites»									
84.60	86.50	FLT									
		« 84.60- 86.50 Flt »« Flt gg 10%»« Flt bx 40%»« Brco 50%»									
86.50	127.80	BSSM									
		BSSM – Backside Siliceous Mudstone Devonian Siliceous Mudstone – Upper Chert Formation Greyish black laminated chert and siliceous mudstone. Randomly-oriented to bedding-parallel bioturbation is common in the bottom of the unit. « lm chrt 75.00-95.00% », « btrb 0.10-2.00cm », < @ 90.50 blk cherty, wormy bands in thickness of 5mm, one seen chert band > < @ 93.00 blk stretches « 99.70- 109.70 broken black mudstone and qt-cal veins Flt »« Flt gg 20%»« Flt bx 40%»« Brco 40%» « 114.20- 114.70 light grey calcareous wormy bands - calcareous bands »									
127.80	256.80	FLMD									
		FLMD – Flaggy Mudstone Formation									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-207

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		Dark grey mudstone in the upper portions of the unit grading into light grey mudstone to siltstone. Contains abundant wispy bioturbation which ranges from randomly-oriented at the top of the unit to bedding-parallel throughout the majority of the unit. Darker upper section has a strong fetid odour along broken surfaces. « btrb 0.10-2.00cm », « cg xtl crns ca 1.00-5.00% 5.00-150.00cm », « crns py 1.00-5.00% 0.10-0.50mm », « medium grey si-mudstone with blk stretched FLMD » « 142.20- 145.60 whitish qt vein with minor calcite and blk clasts qt vein » « 145.80- 146.30 section with dissem. vfg py & silky luster with dewatering? fractures (2 photos) fluid escape structures » < @ 154.00 on bioturbated beds, S0 53° tca > < @ 171.70 on bioturbated beds, S0 27° tca > < @ 182.00 on bioturbated beds, S0 32° tca> < @ 196.10 on bioturbated beds, S0 50° tca> < @ 211.80 on bioturbated beds, S0 53° tca> < @ 226.90 on bioturbated beds, S0 41° tca> < @ 242.50 on bioturbated beds, S0 27° tca>									
256.80	389.60	USMS	632301	386.00	388.00	2.00	0.01	0.24	1.00	5.00	0.04
		USMS – Upper Siliceous Mudstone	632302	388.00	389.60	1.60	0.05	0.33	1.00	10.00	0.15
		Consists of interlaminated dark grey to black mudstone and light to medium grey chert. Regionally, a 1m thick graptolite zone occurs 15m below the top of the upper unit, this is usable as a horizon. The USMS is divided into 3 units. The Lower Unit contains abundant limestone concretions and Galena and sphalerite micro-concretions occur locally near the base of this unit. « gra , lm chrt -20.00% », « cg xtl sph crns ca 5.00-20.00cm », « bed chrt 10.00-15.00% », « interbedded blk mst and medium grey cherty bands, most of the bands are sqiggly, carbonaceous » < @ 294.50 yellowish grey si-mst with thin laminae in length of 20cm laminae >									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-207

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		< @ 296.30 on faint py+qt defined beds parallel to general trend of grey cherty bands and thin py laminae, tca S0 52° > < @ 308.90 on faint beds defined by qt, tca S0 45° > < @ 363.00 on faint graded beds, tca S0 61° > « 263.10- 367.10 carbonaceous laminated mudstone with abundant soft sediment deformation, features. Recrystallized qt -cal veinlets, also this same mineralogy replaces stylolites. Pyrite concretions with rims of qt-cal (up to 2cm di). Strong internal slippage has occurred parallel to S0. Some minor calcareous zones, but mostly just carbonaceous. « 367.10- 368.20 laminated limestone with numerous (1-4mm) veins of titanium -rich euhedral vitreous greenish yellow bladed crystals in calcite matrix. Coarse limestone bands (~10-13cm wide) with brecciated margins, including fine grain limestone fragments. Minor veinlets of calcite, trace disseminated pyrite. Interval laminated at 1-3mm, moderately wavy. « 368.20- 369.50 dark grey carbonaceous mudstone, finely laminated with 2-3mm pyrite laminae. Discontinuous (broken) meandering and splayed calcite veinlets up to 3mm wide. « 359.80- 362.70 broken qt breccia and black mst, Flt »« Flt gg 5%»« Flt bx 10%»« Brco 85%» « 369.50- 369.90 slick-n-lines are evident, Flt »« Flt gg 3%»« Flt bx 97%»« Brco » < @ 371.60 on faint beds defined by py, S0 68° tca> « 369.90- 378.50 carbonaceous mudstone with wormy calcite veins and lighter calcareous veins. In many cases laminae appear convoluted under soft-sed deformation regime. Up to 13mm pyritic veins/beds. « 378.50- 381.50 calcareous mudstone, thicker laminae and abundant mosaic -style calcite veinlets that infill partially some of the fractures. The rock									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-207

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		is friable with abundant spider veins and fractures. « 381.50- 384.25 pyritic limestone with calcite veinlets, laminated S0 55° tca» < @ 383.00 S0 defined by laminae S0 tca 55° > « 387.00- 389.60 carbonaceous mudstone as described with zone of massive limestone with sharp contacts. Heavily brecciated immediately above ACTM, mostly mechanical breaks though. »									
389.60	434.40	ACTM	632303	389.60	390.30	0.70	0.42	0.05	1.00	5.00	8.40
		ACTM – Active Member	632304	390.30	390.90	0.60	1.33	2.20	1.00	200.00	0.60
			632305	390.90	391.40	0.50	5.30	6.54	1.00	620.00	0.81
		The ACTM consists of a repetitive, possibly rhythmic, sequence of intercalated carbonaceous mudstone, cherty mudstone, chert and limestone and locally contains economically significant Zn and Pb sulphides (see bold marked facies), mainly in its sections with well developed lamination. Because of its heterogeneity, the member is distinctive and easily identified.	632306	391.40	391.70	0.30	0.07	0.32	1.00	10.00	0.22
			632307	391.70	392.60	0.90	1.24	8.57	1.00	310.00	0.14
			632308	392.60	393.70	1.10	2.05	6.96	1.00	240.00	0.29
			632309	393.70	394.60	0.90	1.06	7.69	1.00	180.00	0.14
			632310	394.60	394.80	0.20	1.15	2.39	1.00	100.00	0.48
			632311	394.60	394.80	0.20	1.28	2.15	1.00	90.00	0.60
		=====	632312	394.80	395.80	1.00	0.04	0.97	1.00	30.00	0.04
		The ACTM has 8 different facies:	632313	395.80	396.70	0.90	1.24	3.84	1.00	120.00	0.32
		=====	632314	396.70	397.80	1.10	0.03	0.47	1.00	10.00	0.06
			632315	397.80	398.90	1.10	0.13	0.96	1.00	30.00	0.14
		- GREY CHERT FACIES: Consists of laminated medium light grey to medium dark grey chert. Mineralization: 95-99% quartz and up to 5% secondary calcite.	632316	398.90	399.80	0.90	1.20	7.59	1.00	210.00	0.16
			632317	399.80	401.90	2.10	0.01	0.02	1.00	5.00	0.50
			632318	401.90	402.20	0.30	0.01	0.01	1.00	5.00	1.00
		- WHITISH GREY ZN-PB MUDSTONE FACIES: Is a laminated cherty rock containing up to 70% sulphides. Mineralization: quartz, sphalerite and galena are the major minerals with only minor amounts of pyrite and locally calcite. Sedimentary diagenetic structures are common and well displayed in the facies, such as:	632319	402.20	403.40	1.20	0.01	0.01	1.00	5.00	1.00
			632320	403.40	403.40	0.00	0.01	0.01	1.00	5.00	2.00
			632321	403.40	404.60	1.20	0.01	0.01	1.00	5.00	1.00
			632322	404.60	405.40	0.80	0.01	0.01	1.00	5.00	2.00

Selwyn Project Diamond Drill Log

Hole Number:
XYC-207

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
lamination, pseudo-beds, calcite nodules & limestone nodules and abundant water escape structures. Most obvious structure in facies is cross-cutting veins containing massive sphalerite and galena with minor pyrite. They range in width from 0.5 to 10mm. - THIN BEDDED CHERTY MUDSTONE FACIES: Consists of rhythmic intercalated laminae of chert, carbonaceous mudstone and minor micrite. This facies contains significant amounts of Zn and Pb sulphides. - CHERTY MUDSTONE FACIES: Consists of a greyish black monotonous siliceous, carbonaceous mudstone. It is most typically found overlying the thin bedded calcareous mudstone facies. - THIN BEDDED CALCAREOUS MUDSTONE FACIES: Consists of laminated carbonaceous mudstone containing 20-40% calcite, 40-55% quartz and 10-20% muscovite. Sulphides occur in laminae. In the XY area it is usually the lowest facies in the section to contain laminated sulphides. - CALCAREOUS MUDSTONE FACIES: Consists of grey to greyish black monotonous, calcareous siliceous carbonaceous mudstone. There are no feathery calcite beds or pyrite-calcite blebs in the facies, making it easily distinguishable from the CCMS. - GRADED LIMESTONE FACIES: Is a laminated argillaceous limestone with intercalated carbonaceous limestone laminae. The main rock type in the facies is laminated limestone with laminae up to 0.1-7mm thick. - LIGHT GREY BASAL LIMESTONE FACIES - LGLS: Consists of laminated argillaceous limestone. In the Anniv area it marks the end of the ACTM. It's not always present in the stratigraphy. - BASAL FACIES: This is a highly contorted and locally foliated carbonaceous mudstone. Unlike the other facies it is not repeated higher in the member. It			632323	405.40	405.60	0.20	0.01	0.01	1.00	5.00	2.00
			632324	405.60	406.20	0.60	0.80	2.72	1.00	70.00	0.29
			632325	406.20	407.70	1.50	1.79	4.58	1.00	120.00	0.39
			632326	407.70	409.00	1.30	0.74	3.84	1.00	110.00	0.19
			632327	409.00	409.60	0.60	0.32	1.40	1.00	40.00	0.23
			632328	409.60	410.10	0.50	1.45	2.60	1.00	70.00	0.56
			632329	410.10	410.70	0.60	3.80	28.02	5.00	690.00	0.14
			632330	410.70	410.70	0.00	0.92	1.26	216.00	80.00	0.73
			632331	410.70	411.40	0.70	2.15	5.57	3.00	140.00	0.39
			632332	411.40	412.20	0.80	2.48	9.59	3.00	300.00	0.26
			632333	412.20	412.60	0.40	1.41	12.63	4.00	270.00	0.11
			632334	412.60	413.60	1.00	0.38	1.84	1.00	40.00	0.21
			632335	413.60	414.80	1.20	0.03	0.08	1.00	5.00	0.38
			632336	414.80	415.70	0.90	0.01	0.02	1.00	5.00	0.50
			632337	415.70	416.70	1.00	0.34	1.86	1.00	40.00	0.18
			632338	416.70	417.10	0.40	1.62	9.27	4.00	230.00	0.17
			632339	417.10	418.00	0.90	0.07	0.06	1.00	5.00	1.17
			632340	418.00	419.20	1.20	0.04	0.08	1.00	5.00	0.50
			632341	418.00	419.20	1.20	0.04	0.09	1.00	5.00	0.44
			632342	419.20	420.60	1.40	0.47	0.71	1.00	20.00	0.66
			632343	420.60	421.50	0.90	0.06	0.65	3.00	20.00	0.09
			632344	421.50	421.90	0.40	0.05	4.45	3.00	150.00	0.01
			632345	421.90	423.10	1.20	0.06	0.75	3.00	30.00	0.08
			632346	423.10	423.70	0.60	0.03	0.22	3.00	5.00	0.14
			632347	423.70	424.30	0.60	0.03	0.25	1.00	10.00	0.12
			632348	424.30	425.00	0.70	0.12	0.06	2.00	5.00	2.00
			632349	425.00	426.30	1.30	1.24	0.17	9.00	5.00	7.29
			632350	426.30	426.30	0.00	0.01	0.01	1.00	5.00	2.00
			632351	426.30	426.80	0.50	0.12	0.59	3.00	20.00	0.20
			632352	426.80	427.60	0.80	0.08	0.41	3.00	20.00	0.20
			632353	427.60	427.90	0.30	0.37	0.41	5.00	20.00	0.90
			632354	427.90	428.50	0.60	0.43	0.93	7.00	30.00	0.46
			632355	428.50	429.60	1.10	0.10	0.46	3.00	20.00	0.22

Selwyn Project Diamond Drill Log

Hole Number:
XYC-207

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
<i>appears locally to contain the slip zone of a major slump. The facies has only been observed in the YX area. It is 0.1-2m thick. The facies consists of massive carbonaceous siliceous mudstone with lenses and laminae of contorted, slightly carbonaceous chert.</i>			632356	429.60	430.90	1.30	0.06	0.46	5.00	20.00	0.13
			632357	430.90	432.00	1.10	0.15	0.31	5.00	10.00	0.48
			632358	432.00	433.20	1.20	0.01	0.01	1.00	5.00	2.00
			632359	433.20	434.40	1.20	0.01	0.01	1.00	5.00	2.00
« 389.60- 390.30 carbonaceous mudstone, moderately fractured, massive. At least two stages of calcite veining, initial stage is represented by fine tension gashes, later stage overprints initial stage and is associated with qt and brecciated pyrite. Abundant internal slippage has occurred and is represented by slick-n-lines on exposed pseudotachylite. Secondary veining is commonly irregular with a relict stylolitic-style. Stylolites are typically composed of qt + cal and rarely are replaced with sulphide minerals. [Sample 632303] (XRF: Pb-0.339%; Zn-0.064%)											
< @ 389.70 trace amounts of remobilized coarse-grained galena veins >											
« 390.30- 390.90 wavy laminated limestone, discordant veins of qt-cal-sphal-gal. Some veins have blow-outs of coarse-grained galena and sphalerite. Other qt-cal veins have a blebby mineralization. At 390.9m the transition to the next interval is distinctly marked with qt-cal + sphalerite veinlets that truncate the discordant mineralized veins of the lower unit. The contact at base is partially scoured and erosional in nature. [Sample 632304] (XRF: Pb-3.17%; Zn-2.80%; Ti-1.39%)»											
< @ 390.50 laminae S0 40° tca >											
« 390.90- 391.35 medium grey finely laminated mudstone with minor siltstone near the bottom of section where gradeing is observed. Qt-cal tension gashes are more prevalent where siltstone component increases. Specular sphalerite and pyrite. Numerous discordant veinlets of galena. At least two stages of qt-cal alteration, tension gashes are first and are orthoganol to S0 and later replacement of qt-cal that is conformable to S0. In larger qt-veins conformable to S0 pyrite brecciated occurs where pyrite concentration is significant. [Sample 632305] (XRF: Pb-15.17%; Zn-8.26%)»											

Selwyn Project Diamond Drill Log

Hole Number:
XYC-207

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		< @ 390.90 laminae, S0 40° tca> « 391.35- 391.73 Thickly laminated medium grained limestone with some silty layers. Specular sphalerite occurs in secondary qt-cal vein splays. Veins have irregular prorientation and appear more restricted in movement , causing thickening up to 12mm. Limestone may be graded normally in some cases, difficult to be certain though. [Sample 632306] (XRF: Pb-0.119%; Zn-0.412%) » « 391.73- 392.60 Finely laminated and intercalated, normal graded carbonaceous mudstone + siltstone. Upper contact with limestone is defined. Minor brittle failure surfaces have developed psuedotachylite and display slick-n-lines. Laminae are typically 0.2 to 9mm thick. Abundant irregular stylolites of qt-cal +/- trace sphalerite, commonly observed in these features is a brittle fracture pattern that may or may not be infilled with galena-bearing mudstone. Throughout the interval there is disseminated specular pyrite and pyritic qt-bearing micro-concretions. Larger pyrite concretions (up to 2-3cm) commonly have halos of qt-cal. The majority of brittle shearing is of a dextral sense. S0 is highly variable and discontinuous between similar lithology layers that are typ 10-20cm thick, contacts are all scoured but the lithology is the same. This possibly indicated unit thickening under a dextral stress regime and explains the numerous stylolites of qt-cal. [Sample 632307] (XRF: Pb-2.65%; Zn-6.16%) » « 392.60- 393.70 same as abover interval, but with new structural features. Slump-load and flame structures. Numerous galena-bearing discordant veinlets typically orthoganol to laminae and may be associated with micro-shearing. Disseminated specular pyrite and sphalerite. Most sphalerite concentrates in zones of pyritic mudstone and as a result appear slightly yellow. The lithology is a thinly laminated, intercalated mudstone-siltstone with wavy laminae and truncated sections. Qt-cal veins can be extremely irregular, however they splay up-section for the most part. [Sample 632308] (XRF: Pb-2.68%; Zn-6.00%) » « 393.70- 394.60 finely laminated mudstone. The upper 15cm is barren									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-207

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		massive limestone with a defined contact with slightly carbonaceous laminated mudstone. There are many irregular to cusate mm-scale stylolites. Some laminae are pyritic and enriched with sphalerite. Limestone concretions up to 2cm di. Numerous small-scale load/slump structures cause localized ripple-like pattern in laminae. Some evidence of dexteral offset in qt-cal veins. Specular pyrite with trace sphalerite is common (pervasive). Soft-sed slumping causes variations in S0; however it ranges between 70-90 tca. [Sample 632309] (XRF: Pb-1.05%; Zn-5.05%)» « 394.60- 394.80 reverse grading in medium to light grey limestone, with some laminae that are mud-silt-rich. mm-scale pyritic concretions with qt-cal halos, also pervasive disseminated fine-grained pyrite. vfg sphalerite occurs with galena in discordant veins that are typically orthoganol to S0. S0~90 tca but variable. Qt-cal veins have a regular orientation at V2 ~30 tca. [Sample 632310 is original of duplicate; Sample 632311 is duplicate] (XRF: Pb-3.24%; Zn-1.28%) » « 394.80- 395.80 medium to dark grey slightly calareous mudstone, finely laminated and fetid odour . cm-scale bands of pyrite are host to trace fine-grained sphalerite. Minor load casts deform laminae in cases where silt overlies mudstone. Splotches of sphalerite can occur on their own and likely cause up to 1% Zn in the interval. Recrystallized irregular to cusate micro-stylolites appear as a separate event(?) from the qt-cal veining. Galena may become remobilized and finely concentrated in discordant fractures. Evidence of soft-sediment slumping is common and it is along with these slump planes that fractures may become mineralized. Normal grading is evident in laminae. [Sample 632312] (XRF: Pb-0.133%; Zn-1.10%) » « 395.80- 396.70 Finely laminated and intercalated mudstone, siltstone and minor calcareous mudstone. Abundant load structures cause deformation into wavy laminae. Irregularly-shaped pyrite concretions are commonly rimmed with qt-cal and pyritic bands up to 12mm do occur. Soft-sed slumping initiated micro tear faults that serve as an avenue for late-stage remobilized base metals. Recrystallized qt occurs on late stage qt-veins. Square to cusate stylolites can also serve as remobilization avenues. Within this interval there									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-207

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		are layers that truncate the lower layers and this causes an apparent cross-bedding attitude. [Sample 632313] (XRF: Pb-0.536%; Zn-2.24%)» « 369.70- 397.80 Finely laminated medium grey mudstone with cm-scale limestone concretions that host pyritic veins. Sphalerite is very finely disseminated in laminae that have a higher sulphide content. Discordant fractures are not mineralized. Stylolites are irregular to cusped and have been recrystallized with calcite +/- quartz, in some cases they have grown in thickness significantly and appear wormy. Some laminae display normal grading. Limestone concretions are up to 5cm long and sediment is deformed around them --> maybe they are actually clasts or syn-depositional concretions? [Sample 632314] (XRF: Zn-0.576%) » < @ 369.70 consistent laminae, S0 75° tca> « 397.80- 398.85 Massive to laminated carbonaceous mudstone. cm-scale concretions with calcite-quartz veins. Veins of calcite-quartz have fibrous intergrowths that indicate sigma 3 is roughly orthogonal to S0 ~80 tca. Irregular stylolites are conformable to S0 and can be replaced by pyrite, quartz, calcite or any combination of the three. Pyrite concretions up to 2cm. Partially boudinaged pyritic bands are associated with fine-grained sphalerite. [Sample 632315] (XRF: Pb-0.136%; Zn-0.752%) » « 398.40- 398.85 lots of breccia with SLS, increases in veining Flt »« Flt gg »« Flt breccia 100%»« Breccia » « 398.85- 399.80 Transitional from greyish black massive carbonaceous mudstone to a dark grey slightly calcareous laminated mudstone to grey calcareous finely laminated mudstone. Abundant soft-sed deformation structures. Especially where laminae are more prominent. Disseminated fine grained pyrite forms along S0 with quartz +/- calcite. Fine-grained sphalerite occurs in some of the laminae with an increase in sulphide minerals. mm-cm-scale pyrite concretions may or may not have calcite-quartz rims. Slickensides are evident along S0, S0 is variable. Remobilized galena occurs in fractures and with sphalerite in sphalerite-rich zones. [Sample 632316] (XRF: Pb-1.79%;									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-207

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		Zn-3.04%)» « 399.80- 401.80 Grey, weakly laminated limestone with some layers of coarser recrystallized limestone occurring with pyrite. Radiating pattern to some qt-cal veins, disseminated pyrite and pyrrhotite is specular and partially localized. Laminae are visible when sulphide mineral content increases. [Sample 632317] (XRF: Pb-0.090%; Zn-0.117%; Mn-0.221%) » < @ 399.80 laminae, S0 35° tca> « 401.90- 402.20 limestone appears massive and recrystallized Flt »« Flt gg »« Flt bx 100%» [Sample 632318] (XRF: Pb-0.132%)» « 402.20- 403.40 Fine crystalline limestone with qt-cal veinlets and pyritic veinlets. Two veining stages, early stage cut at low oblique angle to S0 and late stage are irregular. S0 is largely defined by sulphide minerals. [Sample 632319 & BLNK 632320 BLNK] (XRF: Pb-0.09%)» « 403.40- 404.60 Same limestone as previously described for sample 318, 319; however, there is a void structure in this interval that is filled with a yellowish, euhedral crystal that has a high amount of Ti and V. The crystals are euhedral, up to 5mm long, cleavage faces have striae, habit is drusy with monoclinic sharp-edged tabular, twinned, vitreous, translucent crystals. I think this mineral is titanite. [Sample 632321] (XRF: V-2.02%; Ti-4.87%) » « 404.60- 405.40 Crystalline limestone, grading into a dirty fine grained mud-rich limestone lower down in the interval. Veins are slightly oblique to pressure dissolution seams which have regular orientation at ~25 tca. Very weakly disseminated sulphides help define S0. [Sample 632322] (XRF: Barren)» < @ 404.60 defined by sulphides mostly, S0 32° tca> « 405.40- 405.60 Coarse crystalline limestone, massive, with fine qt-cal									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-207

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		veinlets. There is a structure in this interval that looks like broken up and compacted fossiliferous? material. [Sample 632323] (XRF: Barren)» « Slightly carbonaceous finely laminated mudstone with pyritic bands up to 1.3cm wide, blebby sphalerite and concordant galena mineralized micro-fractures. Some minor zones of massive pyrite with blebby sphalerite. Most veining is conformable with S0. [Sample 632324] (XRF: Pb-1.31%; Zn-1.42%) » < @ 405.60 laminae, S0 25° tca> « 406.20- 407.70 Carbonaceous and calcareous, laminated mudstone, intercalated with laminae of fine grained limestone. Abundant cusped stylolites and some irregular, most have recrystallized qt +/- calcite replacing original mineralogy. Mico-concretions of pyrite and sphalerite. High concentrations of sulphides are often associated with sphalerite. S0 indicated a cross bedding scoured relationship between depositional events. Abundant soft-sed deformation and qt-cal veins. Galena mineralization can occur as blow outs from pressure dissolution seams and becomes coarse-grained + blebby. Some areas have slightly deformed limestone concretions. [Sample 632325] (XRF: Pb-1.01%; Zn-2.99%)» « 407.70- 409.00 Finely laminated muddy limestone, partially boudinaged sphalerite laminae. Abundant stylolites, typ hjagged and infilled with qt-cal. Galena appears remobilized and occasionally blows out into cm-scale gobs discordant to S0. When this happens it is associated with grain-size increases. Voided veins have euhedral titanite crystals with enrichments of Vanadium. Laminae exhibit soft sed deformation. mm-cm-scale limestone concretions are common. [Sample 632326] (XRF: Pb-0.754%; Zn-2.19%; V-0.665%; Ti-1.74%)» < @ 407.70 consistent laminae S0 35° tca> « 409.00- 409.60 Calcareous , carbonaceous, laminated mudstone, normal graded sections. cm-scale limestone concretions. Minor fault in upper									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-207

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		interval. Soft-sed deformation. Two vein events and a qt-recrystallization phase that cases coarsening. Specular trace dissem pyrite + sphalerite. [Sample 632327] (XRF: Pb-0.467%; Zn-0.798%) » « 409.60- 410.10 Calcareous and carbonaceous, laminated mudstone, upper interval has massive pyrite with trace pyrrhotite ~3.3cm thick. Cuspate stylolites. There are soft-sed fluid escape structures that form flame structures in laminae and are directly orthogonal to S0. The escape structures are mineralized with remobilized galena. [Sample 632328] (XRF: Pb-1.34%; Zn-2.6%)» « 409.90- 410.10 Flt »« Flt gg 100%»« Flt bx »« Brco » « 410.10- 410.70 Calcareous mudstone, finely laminated mudstone and sphalerite. mm-scale pressure dissolution fractures are infilled with galena. Abundant soft-sed slumping. Limestone aggregate at lower part of section in addition to convoluted laminae. In addition to laminae of up to 90% sphalerite there are blebs of sphalerite. This is a high grade interval. [Sample 632329; STD-A 632330 STD-A] (XRF: Pb-9.38%; Zn-24.82%) » « 410.70- 411.40 Calcareous and carbonaceous laminated mudstone, some laminae are highly enriched with sphalerite, up to 30-50% locally. Some layers are more calcareous than others, lobate limestone fragments (or concretions?). Soft-sed brittle and ductile deformation is evident. Galena tends to be remobilized mostly and can occur interstitially to fine grained sphalerite. [Sample 632331] (XRF: Pb-2.02%; Zn-3.12%)» « 411.40- 412.20 Calcareous and carbonaceous intercalated mudstone with varying amounts of sphalerite in laminae, up to 30-40% in some localized zones. Abundant soft-sed deformation and fluid escape structures. Sphalerite blebs and layers are evident. Disseminated pyrite, limestone concretions on a cm-scale. Galena appears to be remobilized in pressure dissolution seams and is interstitial to sphalerite. [Sample 632332] (XRF: Pb-2.32%; Zn-7.41%) »									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-207

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		< @ 411.40 consistent laminae, S0 58° tca> « 412.20- 412.60 Calcareous and carbonaceous laminated mudstone with large limestone concretions and fragmental limestone concretions. Some layers are very sphalerite -rich. Oblique recrystallized qt-cal veins, in some areas they are boudinaged. [Sample 632333] (XRF: Pb-2.02%; Zn-3.12%) (XRF: Pb-1.64%; Zn-6.56%)» « 412.60- 413.60 Calcareous mudstone to muddy limestone, laminated, cm-scale concretions. Many fractures are infilled with cal-qt, titanite, a bluish mineral (anhydrite?). Soft-sed deformation features are common. Minor stylolites are infilled with qt. [Sample 632334] (XRF: Pb-0.479%; Zn-0.847%) » « 413.60- 414.80 Dirty limestone, massive to laminated with demagnetized pyrrhotite, recrystallized calcite and qt mark major depositional boundaries. Minor pyrite blebs. Cal-qt veins may also be discordant to S0, where rock is not massive. [Sample 632335] (XRF: Pb-0.077%; Zn-0.065%) » « 414.80- 415.80 Laminated dirty limestone as previous sample. Near lower part of the interval, limestone concretions increase in abundance and host rock is mud-rich. Some laminae sequences have increases of sulphide minerals up to 15% with minor sphalerite and interstitial galena. Discordant micro-stringers of demagnetized pyrrhotite. [Sample 632336] (XRF: Pb-0.078%; Zn-0.079%; Mn-0.233%)» « 415.70- 416.70 Laminated calcareous mudstone with light and dark laminae, lighter bands are sphalerite-rich. Most cal-qt veins are conformable to S0 and mark depositional boundaries. Minor soft-sed deformation features. Thicker veins have blebs of sphalerite +/- pyrite on a mm-scale. Stylolites have very low amplitude. [Sample 632337] (XRF: Pb-0.435%; Zn-1.6%; V-0.434%)» « 416.70- 417.10 Highly base-metal mineralized section of finely laminated mudstone. Strong soft-sed deformation features such as load slumping									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-207

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		, density shifts, stylolites (now infilled with qt-cal). Lower part of interval has more mud and slightly less sphalerite. In high sulphide zones qt-cal is chaotic mostly but attempts to mimic SO. [Sample 632338] (XRF: Pb-1.14%; Zn-5.11%)» < @ 416.70 consistent laminae, S0 47 tca> « 417.10- 418.00 Laminated calcareous mudstone, slightly carbonaceous. Semi-massive bands of yellowish pyrite are offset by brittle sinistral faults. Fractures are infilled with calcite and bluish anhydrite? +/- qt. Pressure dissolution seams often host visible galena that has been remobilized. [Sample 632339] (XRF: Pb-0.099%)» < @ 417.10 consistent laminae, S0 40° tca> « 418.00- 419.20 Strngly calcareous laminated mudstone. Stylolites exhibit primary features . Limestone concretions on cm-scale are stretched out along S0. Pyrite bands are relatively minor. Galena is remobilized in fractures. [Sample 632340; DPLICT 632341 DPLICT] (XRF: Pb-0.194%; Zn-0.155%)» < @ 418.00 consistent laminae, S0 35° tca> « 419.20- 420.60 Laminated mudstone, slightly calcareous and carbonaceous. Seoft-sed deformation, load structures and folds. Limestone concretions have compositional zoneing with at least one layer of sulphide-rich minerals, including sphalerite. Upper-interval has ~4cm thick section of sphalerite-rich bands, up to 10% but most sphalerite and galena appears to be secondary and remobilized into concretions and blebs. This interval documents a hinge region to a fold and S0 is therefore highly variable. [Sample 632342] (XRF: Pb-0.171%; Zn-0.155%) » « 420.60- 421.50 Section os laminated mudstone that is highly syndepositionally deformed, with abundant square to cusate and irregular stylolites. Coarse-grained limestone concretions sometimes exhibit internal									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-207

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		laminae. Pyritic mudstone +/- sphalerite appears to embay the limestone concretion boundaries. S0 is too variable to measure. Some recrystallized qt-veins have brecciated massive pyrite sections +/- sphalerite. [Sample 632343] (XRF: Pb-0.113%; Zn-0.510%) » « 421.50- 421.90 Carbonaceous and slightly calcareous laminated mudstone with psuedotachylite near lower interval showing slick-n-lines. Minor qt-cal veining and some sphalerite-rich laminae which tend to be lighter in colour. Pyrite concretions border between mm-cm-scale and appear framboidal in some cases. This zone is also partially silicified which helps to obliterate S0. [Sample 632344] (XRF: Pb-0.214%; Zn-0.480%)» « 421.90- 423.10 Strongly calcareous mudstone with disseminated coarse pyrite in some layers. A few stretched out laminated limestone concretions. Some sulphide rich bands with sphalerite concretions/blebs and a secondary sulphidization event produces coarse disseminated pyrite which overprints sulphide-rich laminae. A few irregular micro-stylolites and highly variable S0 which may position this interval near a fold hinge. This unit could get away with being called a dirty limestone intercalated with mudstone. [Sample 632345] (XRF: Pb-0.261%; Zn-0.499%; Ti-.925%)» « 423.10- 423.70 Laminated dirty limestone with abundant pyrite veins that have been brecciated and boudinaged by qt and minor cal and then later recrystallized. Limestone is coarse grained and internally folded in a recumbant fashion on a small scale. Disseminated pyrite is pervasive. S0 is highly variable. [Sample 632346] (XRF: Pb-0.093%; Zn-0.170%)» « 423.70- 424.30 Slightly carbonaceous, laminated limestone. Some discordant veining of qt-cal and blebs of sphalerite which are rare. Voided fractures have euhedral crystals of calcite tinged blue by anhydrite impurities? qt-is also euhedral. At least two veining events took place, one slightly oblique to S0 and the other nearly orthogonal. Fractures show graphitic slick-n-lines. Near base of interval pyritic bands are slightly boudinaged. [Sample 632347] (XRF: Pb-0.114%; Zn-0.282%) »									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-207

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		« 424.30- 425.00 Graptolitic limestone horizon. The horizon is interrupted by a semi-massive pyrite band ~4cm thick lower in the interval. Graptolites are all in aligned orientation on S0 and therefore we only see the short cross-section of them, this appear somewhat circular in shape. Even the sulphide rich bands have remineralized the graptolites. The limestone in this section is relatively coarse grained and the interval is so obvious this may be a good marker horizon. [Sample 632348] (XRF: Pb-0.123%; Zn-0.273%) » « 425.00- 425.60 Intercalated carbonaceous mudstone with laminated limestone. Conformable qt-cal veinlets and veins that are typ associated with pyrite. Concretionary pyrite is common and disseminated specular pyrite is pervasive, sometimes enriching laminae with coarse pyrite. Many veinlets are also irregular with many minor folds? or deviations from a plane, which could be reminerallized stylolites. [Sample 632349; BLNK 632350 BLNK] (XRF: Pb-0.167%; Zn-0.083%)» < @ 425.00 consistent laminae, S0 28° tca> « 426.30- 426.80 Muddy, laminated limestone, pyrite-rich laminae occur with increases in sphalerite content. Irregular micro-stylolites, pyrite concretions with qt-cal rims. [Sample 632351] (XRF: Pb-0.307%; Zn-0.965%) » « 426.80- 427.60 Carbonaceous and strongly calcareous mudstone to muddy limestone, finely laminated. Sulphide-rich bands are often associated with recrystallized qt-cal. Trace dissem pyrite is pervasive. Veining is minor but appears deformed and stretched in a conformable fashion to S0. [Sample 632352] (XRF: Pb-0.142%; Zn-0.237%)» « 427.60- 427.90 Calcareous and carbonaceous mudstone with deformed laminae and remineralized stylolite swarms. S0 is syn-depositionally deformed and galena +/- sphalerite is remobilized in discordant fractures. [Sample 632353] (XRF: Pb-0.816%; Zn-0.101%)» « 427.90- 428.50 Carbonaceous, calcareous, and slightly silicified									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-207

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		laminated mudstone. cm-scale pyrite bands. Abundant internal brittle deformation causes slick-n-lines on psuedotachylite surfaces. Minor micro-stylolite swarms are typ remineralized by calcite, as are the micro-tension gashes. [Sample 632354] (XRF: Pb-0.611%; Zn-0.591%)» « 428.50- 429.60 Slightly calcareous, carbonaceous laminated mudstone that is highly internally fractures. Most fractures are infilled with cal - qt. Stylolite breccia and swarms break up the laminated mudstone. Abundant recrystallized qt, also psuedotachylite on fault surfaces. [Sample 632355] (XRF: Pb-0.176%; Zn-0.305%) » « 429.60- 430.90 Carbonaceous and slightly calcareous laminated silicified mudstone, slick-nlines on psuedotachylite, numerous conformable qt-cal veins and remineralized stylolites. Pyritic disseminations are pervasive and associated with trace fine grained sphalerite. [Sample 632356] (XRF: Pb-0.147%; Zn-0.179%) » < @ 429.60 consistent laminae, S0 30° tca> « 430.90- 432.00 Flt »« Flt gg »« Flt bx 85%»« Brco 15%» « 430.90- 432.00 Carbonaceous and slightly calcareous laminated mudstone. In the breccia zone there are some semi-massive sulphide fragments. [Sample 632357] (XRF: Pb-0.207%; Zn-0.402%)» « 432.00- 433.20 Defined contacts at interval top with mudstone above and a bioturbated basal limestone beneath. This interval is the basal limestone unit of the active member and exhibits stretched out limestone concretions and sulphide blebs that are conformable to S0. Recrystallized qt-cal veins. S0 is at very low angle, trending to 0, indicated we could be in the hinge region of a fold structure. [Sample 632358] (XRF: Zn-0.093%)» « 433.20- 434.40 Massive to weakly laminated limestone, pyrite concretions and disseminations are common, as are irregular stylolites that are infilled with calcite . Very faint bioturbation features are randomly									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-207

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		oriented near the bottom of the interval. [Sample 632359; STD-B 632360 STD-B] (XRF: Barren)»									
434.40	470.90	CCMS	632360	434.40	434.40	0.00	1.51	4.34	29.00	270.00	0.35
		CCMS – Calcareous Mudstone	632361	434.40	435.50	1.10	0.01	0.01	1.00	5.00	2.00
			632362	435.50	436.30	0.80	0.01	0.01	1.00	5.00	2.00
			632363	436.30	438.00	1.70	0.01	0.09	7.00	5.00	0.11
		Massive, calcareous, carbonaceous, dark grey mudstone. Most of the member is massive, but rare poorly defined bedding and pyrite-calcite micro-concretions are present. Most diagnostic structures are feathery calcite beds (=thin calcite-cemented concretions, many of them contain pyrite cores) and calcite pseudo-beds (= fibrous calcite vein parallel to bedding). « lm ca 5.00-10.00mm », « nodules py -3.00% 2.00-20.00mm », « 434.40- 435.50 Massive to weakly laminated calcareous, carbonaceous dark grey mudstone, conchoidal fractures, limestone concretions, and micro-pyrite +/- cal concretions. Disseminated sulphides help to outline the soft-sed deformation and laminae. [Shoulder Sample 632361] (XRF: Barren) » « 435.50- 436.30 Calcareous mudstone to muddy limestone with abundant stylolite swarms and qt-cal veins associated with brecciated massive pyrite. Wispy cal veins help define a variable S0 but for the most part the laminae are poorly defined . Abundant psuedotachylite on fracture planes with slick-n-lines. [Sample 632362] (XRF: Barren)» « 436.30- 438.00 Strongly carbonaceous massive mudstone with pyritic concretions and blebs that may help to define a weak S0. Also , wispy cal veinlets are conformable and can be associated with increases in sulphides. [Sample 632363] (XRF: Barren)» « 438.00- 446.40 Fissile carbonaceous mudstone. sSilicification is moderate to strong. Disseminated specular sulphides (pyrite +/- pyrrhotite) is pervasive and helps to define laminae. Pyritic concretions can be irregular in shape and may be replacing micro fold structures. Some beds show normal gradeing. Pyritic laminae of varying mm-scale laminae typically occur with cal and qt. Extremely thin calcite veinlets conformable to S0 help to define S0.»									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-207

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		« 446.40- 448.70 bluish tint to calcite, lots of pseudotachylite and SLS Flt »« Flt gg 35%»« Flt bx 60%»« Brco 5%» < @ 451.20 wispy calcite defined laminae, tca S0 40° > « 448.70- 464.70 same fissile mudstone as described above the fault. Calcite-rich laminae help to define S0. Pyritic concretions are common and have calcite-qt veins sometimes. In lower part of the interval there are stylolite swarms and breccias that increase the rocks susceptibility to brittle failure. The rock is still siliceous, causing many fissile and concoidal machine breaks. » « 464.70- 465.10 Flt »« Flt gg 33%»« Flt bx 33%»« Brco 33%» « 465.10- 470.90 Siliceous, fissile, carbonaceous and slightly calcareous pyritic mudrock showing great evidence of normal grading (if the unit is not overturned). Abundant remineralized stylolites and pressure dissolution seams . This unit has undergone lots of internal slippage causing abundant psuedotachylite to develop with or without slick-n-lines. »									
470.90	470.90	EOH									

Diamond Drill Log

Comprehensive Report for Hole:

XYC-206

Hole No.: XYC-206	Depth: 445.40 m	Horizontal Length: 0.00 m	Project: 1710
Location Data:			
Property:	Selwyn Project	Claim Name:	X 13
Mining District:	Selywn Basin	Grant Number:	Y64538
Province/Territory:	Yukon		
UTM Co-Ordinates & Altitude of Drill Hole Collar:			
UTM Easting:	488951.17 m	True Azimuth:	335.0 °
UTM Northing:	6926567.67 m	Hole Angle:	-82.0 °
Elevation (m):	1689.00 m	NTS Name:	Placer Creek
		NTS Number:	105I06
Grid Co-Ordinates of Drill Hole Collar:			
Grid Easting (m):	0.00 m	Grid Name:	HP 06
Grid Northing (m):	0.00 m	Grid Type:	100m
Grid Azimuth:	35.0 °		
Dimond Drilling Contract:			
Drilled By:	NL-03	Date Drilling Start:	09/03/2010
		Date Finish:	09/10/2010
Diamond Drill Core:			
Logged By:	Kate Cameron	Date Logging Start:	09/11/2010
		Date Finish:	09/19/2010
Legend for Core Logging Codes: PAX			
Core Size:	NQ/NQ3	Cemented:	Yes
Casing Depth:	11.30 m	Casing Pulled:	Yes
Water Depth:	0.00 m	Overburden Depth:	11.30 m
Level:	Section:	Drift:	

Selwyn Project

Diamond Drill Log

Survey Data for Hole

XYC-206

Hole Comments:

Sat, Sep 04 --- XYC-204 got shut down yesterday afternoon after passing 430m, without hitting the ACTM or the fault. The drill got spun to another azimuth around evening shift change and drilling started around 9pm. 37' of casing was put in and they drilled up to a depth of 39m. Right now in BSSM. Core is badly broken up from 15m to 27m.

=====

Sun, Sep 05 --- Drilling is going very well. During the past 24hrs, 139m of core got drilled. Night shift was not able to take all core drilled during their shift back to Don Camp. At 149m (last box they could take with them) the core was FLMD. Right now without mudmixer, but looking at the footage, it doesn't affect the drilling.

=====

Mon, Sep 06 --- At morning shift change the total depth was 260m and in USMS.

=====

Tue, Sep 07 --- At morning shift change the total depth was 325m and still in USMS.

=====

Wed, Sep 08 --- In ACTM right now. Poorly mineralized and rich in limestone. At morning shift change the total depth of the hole was at 360m. The first mineralization was seen at approximately 328m.

=====

Thu, Sep 09 --- Currently at 408 meters, in blocky, faulted, largely unmineralized mudstone. Last mineralization observed at 392 meters. We may be in what will be logged as CCMS, but it is not typical footwall, so we will drill through at least part of day shift to see if we hit any more mineralization. I will check the core around mid-day, and make a decision then.

=====

Fri, Sep 10 --- Shut down the hole this morning in CCMS at 445.31meters. The core was very blocky, and has resulted in fairly slow drilling over the past 24 hours (37 meters). The ACTM-CCMS contact is at approximately 427 meters, though ACTM for several meters above that contact is unmineralized. They are now pulling rods and cementing, and we will move to the highest slope setup, #16 (XYC-208) late this morning.

<i>Depth</i>	<i>Dip</i>	<i>Azimuth</i>
0.00	-82.0	335.0
48.20	-81.4	335.9
93.90	-81.4	336.7
139.60	-80.9	337.8
185.30	-80.2	336.1
231.00	-78.5	343.9
276.50	-77.4	342.1
322.50	-77.3	358.1
366.10	-77.4	1.1
411.80	-77.6	348.0
445.30	-77.5	5.6

Selwyn Project Diamond Drill Log

Hole Number:
XYC-206

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
0.00	11.30	OVBR									
11.30	131.70	BSSM									
BSSM – Backside Siliceous Mudstone											
Devonian Siliceous Mudstone – Upper Chert Formation											
Greyish black laminated chert and siliceous mudstone. Randomly-oriented to bedding-parallel bioturbation is common in the bottom of the unit. « lm chrt 75.00-95.00% », « btrb 0.10-2.00cm »,											
Bedding is difficult to find due to lack of features. Calcite veining is common 2mm to 2.5 cm wide. Highly carbonaceous unit, with some calcareous sections. Unit is not competent.											
« 15.40- 16.00 FLT »« brco 70%»« flt bx 20%»« flt gg 10%»											
« 18.10- 20.20 FLT »« brco 30%»« flt bx 50%»« flt gg 20%»											
« 20.50- 23.80 FLT »« brco 30%»« flt bx 50%»« flt gg 20%»											
« 24.80- 26.50 FLT »« brco 50%»« flt bx 40%»« flt gg 10%»											
« @ 29.20 S0 in cherty bands TCA 40° »											
« 36.10- 41.00 Reconstituted flt bx, cemented with calcite. »											
« 44.50- 46.20 FLT »« brco 20%»« flt bx 75%»« flt gg 5%»											
« 50.60- 52.60 FLT »« brco 20%»« flt bx 70%»« flt gg 10%»											
« 53.40- 54.90 FLT »« brco 75%»« flt bx 20%»« flt gg 5%»											
« 59.20- 61.60 FLT »« brco 30%»« flt bx 65%»« flt gg 5%»											
« 62.30- 64.50 FLT »« brco 10%»« flt bx 65%»« flt gg 25%»											
« 68.10- 75.90 FLT zone. Breakage along planes of weakness at calcite veins. »« brco 40%»« flt bx 50%»« flt gg 10%»											
« 76.80- 77.00 Reconstituted flt bx. Black mudstone cemented by calcite. »											
« 77.00- 78.00 FLT »« flt bx 90%»« flt gg 10%»											
« 84.40- 102.10 FLT Large fault zone, mostly breccia. The broken core looks like reconstituted flt bx cemented by calcite. »« brco 20%»« flt bx 50%»« flt gg 30%»											
« 114.00- 126.10 FLT zone. »« brco 20%»« flt bx 65%»« flt gg 15%»											

Selwyn Project Diamond Drill Log

Hole Number:
XYC-206

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		« 128.40- 131.70 Reconstituted flt bx and gg, cemented with quartz and calcite. »									
131.70	215.30	FLMD									
FLMD – Flaggy Mudstone Formation											
Dark grey mudstone in the upper portions of the unit grading into light grey mudstone to siltstone. Contains abundant wispy bioturbation which ranges from randomly-oriented at the top of the unit to bedding-parallel throughout the majority of the unit. Darker upper section has a strong fetid odour along broken surfaces. « btrb 0.10-2.00cm », « cg xtl crns ca 1.00-5.00% 5.00-150.00cm », « crns py 1.00-5.00% 0.10-0.50mm », Very competent unit. Bedding defined by darker and lighter layers of mudstone. Very little calcite, occurring only in veins. Traces of fine pyrite disseminated throughout.											
« 132.70- 146.00 Reconstituted flt bx cemented by calcite and quartz. Sections that are not flt bx are strongly deformed. Clasts are exclusively angular to sun-angular, flaggy mudstone, 0.5 mm to 3.0 cm.»											
« 132.70- 159.60 FLT Broken core dominates; slick n slides are present. FLT »« brco 80%»« flt bx 20%»											
« 165.60- 166.20 Fault. Abundant calcite veining, and associated pyrite. FLT »« brco 90%»« flt bx 10%»											
« @ 168.00 S0 in dark laminae S0 TCA 30° »											
« 179.90- 180.40 FLT »« flt bx 100%»											
« @ 185.60 S0 TCA 15-20° »											
« 192.50- 195.00 Reconstituted flt bx cemented by calcite. »											
« 215.20- 217.50 FLT »« brco 10%»« flt bx 70%»« flt gg 20%»											
215.30	324.20	USMS	632651	321.50	323.00	1.50	0.02	0.87	1.00	30.00	0.02
USMS – Upper Siliceous Mudstone			632652	323.00	324.20	1.20	0.31	0.51	1.00	30.00	0.61
Consists of interlaminated dark grey to black mudstone and light to medium grey											

Selwyn Project Diamond Drill Log

Hole Number:
XYC-206

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		chert. Regionally, a 1m thick graptolite zone occurs 15m below the top of the upper unit, this is usable as a horizon. The USMS is divided into 3 units. The Lower Unit contains abundant limestone concretions and Galena and sphalerite micro-concretions occur locally near the base of this unit. « gra , lm chrt -20.00% », « cg xtl sph crns ca 5.00-20.00cm », « bed chrt 10.00-15.00% », Classic. « 218.52- 221.90 FLT » « 218.52- 221.90 brco 20%»« flt bx 60%»« flt gg 20%» « @ 226.00 Faint light grey banding and elongated mm-scale blebs of calcite. S0 TCA 25° » « @ 227.30 Light grey banding; pyrite and calcite laminae. S0 TCA 35° » « 235.70- 235.90 FLT »« flt bx 60%»« flt gg 40%» « 244.60- 246.30 FLT »« brco 60%»« flt bx 25%»« flt gg 15%» « 257.30- 260.30 Fault. Slick n slides present. FLT »« brco 10%»« flt bx 55%»« flt gg 35%» « 261.00- 262.40 Fault. Slick n slides present. FLT »« brco 40%»« flt gg 60%» « 264.90- 267.70 FLT »« brco 10%»« flt bx 60%»« flt gg 30%» « @ 269.30 Laminae of black and dark grey muddy material. S0 TCA 35° » « 269.70- 270.70 Galena occuring with coarse sphalerite, and associated with calcite veining. Ga, Sph » « 274.70- 276.70 FLT »« brco 75%»« flt bx 5%»« flt gg 20%» « 282.00- 285.40 Fault. Slick n slides present. FT »« brco 30%»« flt bx 70%» « 286.80- 287.80 FLT »« flt bx 100%» « 292.00- 294.00 Fault. Slick n slides present. FT »« brco 50%»« flt bx 40%»« flt gg 10%» « @ 304.20 Local blebs of veiny calcite contain abundant pyrite and galena.									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-206

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
Galena occurs as small, well formed crystals. Metallics are mobilized in with calcite . > « 305.40- 306.00 FLT »« flt bx 95%»« flt gg 5%» « 308.00- 309.50 FLT »« brco 40%»« flt bx 45%»« flt gg 15%» < @ 310.00 Laminae containing pyrite and brownish mud. S0 TCA 60-65° > < @ 316.00 Bedding in cherty bands. S0 TCA 40° > « 316.90- 318.90 Fault/shear zone. FLT »« brco 75%»« flt bx 10%»« flt gg 15%» « 320.40- 321.60 FLT » «brco 90%»« flt bx 10%» < @ 323.00 Bedding in cherty laminae. S0 TCA 40° > « 323.40- 324.20 FLT »« brco 70%»« flt bx 25%»« flt gg 5%»											
324.20	427.20	ACTM	632653	324.20	324.70	0.50	2.85	9.04	3.00	520.00	0.32
ACTM – Active Member			632654	324.70	324.80	0.10	0.22	0.05	1.00	5.00	4.40
			632655	324.80	325.00	0.20	3.04	12.46	5.00	430.00	0.24
The ACTM consists of a repetitive, possibly rhythmic, sequence of intercalated carbonaceous mudstone, cherty mudstone, chert and limestone and locally contains economically significant Zn and Pb sulphides (see bold marked facies), mainly in its sections with well developed lamination. Because of its heterogeneity, the member is distinctive and easily identified.			632656	325.00	325.30	0.30	1.79	10.44	3.00	390.00	0.17
			632657	325.30	326.10	0.80	2.21	10.67	3.00	410.00	0.21
			632658	326.10	326.70	0.60	0.32	1.10	1.00	40.00	0.29
			632659	326.70	327.30	0.60	0.93	6.09	2.00	150.00	0.15
			632660	327.30	328.60	1.30	0.49	3.80	1.00	100.00	0.13
			632661	327.30	328.60	1.30	0.37	3.70	1.00	100.00	0.10
=====			632662	328.60	329.50	0.90	0.06	0.75	1.00	20.00	0.08
The ACTM has 8 different facies:			632663	329.50	330.30	0.80	0.01	0.29	1.00	5.00	0.03
=====			632664	330.30	330.50	0.20	0.01	2.15	1.00	80.00	0.00
- GREY CHERT FACIES: Consists of laminated medium light grey to medium dark grey chert. Mineralization: 95-99% quartz and up to 5% secondary calcite.			632665	330.50	330.60	0.10	0.01	0.01	1.00	5.00	2.00
			632666	330.60	331.60	1.00	0.01	0.11	1.00	5.00	0.09
- WHITISH GREY ZN-PB MUDSTONE FACIES: Is a laminated cherty rock containing up			632667	331.60	332.50	0.90	0.02	0.72	1.00	20.00	0.03
to 70% sulphides. Mineralization: quartz, sphalerite and galena are the major minerals with only minor amounts of pyrite and locally calcite. Sedimentary diagenetic structures are common and well displayed in the facies, such as:			632668	332.50	333.30	0.80	0.01	0.58	1.00	20.00	0.02
lamination, pseudo-beds, calcite nodules & limestone nodules and abundant water escape structures. Most obvious structure in facies is cross-cutting veins			632669	333.30	333.60	0.30	0.01	1.48	1.00	50.00	0.01
containing massive sphalerite and galena with minor pyrite. They range in width											
			632670	333.60	333.60	0.00	0.01	0.01	1.00	5.00	2.00
			632671	333.60	334.50	0.90	0.01	0.66	1.00	20.00	0.02
			632672	334.50	334.90	0.40	0.01	0.18	1.00	5.00	0.06
			632673	334.90	336.20	1.30	0.06	1.22	1.00	40.00	0.05
			632674	336.20	337.80	1.60	0.05	0.89	1.00	30.00	0.06
			632675	337.80	338.00	0.20	0.43	2.94	1.00	100.00	0.15

Selwyn Project Diamond Drill Log

Hole Number:
XYC-206

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
from 0.5 to 10mm.			632676	338.00	338.70	0.70	0.13	0.21	1.00	5.00	0.62
- THIN BEDDED CHERTY MUDSTONE FACIES: Consists of rhythmic intercalated laminae of chert, carbonaceous mudstone and minor micrite. This facies contains significant amounts of Zn and Pb sulphides.			632677	338.70	338.90	0.20	13.52	4.41	6.00	160.00	3.07
			632678	338.90	340.00	1.10	0.34	1.68	1.00	60.00	0.20
			632679	340.00	340.50	0.50	0.04	1.12	1.00	40.00	0.04
			632680	340.50	340.50	0.00	1.44	4.35	28.00	290.00	0.33
- CHERTY MUDSTONE FACIES: Consists of a greyish black monotonous siliceous, carbonaceous mudstone. It is most typically found overlying the thin bedded calcareous mudstone facies.			632681	340.50	340.70	0.20	0.03	0.37	1.00	10.00	0.08
			632682	340.70	342.40	1.70	0.50	0.85	1.00	30.00	0.59
			632683	342.40	343.10	0.70	0.04	0.09	1.00	5.00	0.44
			632684	343.10	344.30	1.20	1.39	9.24	2.00	260.00	0.15
- THIN BEDDED CALCAREOUS MUDSTONE FACIES: Consists of laminated carbonaceous mudstone containing 20-40% calcite, 40-55% quartz and 10-20% muscovite. Sulphides occur in laminae. In the XY area it is usually the lowest facies in the section to contain laminated sulphides.			632685	344.30	346.10	1.80	0.32	0.25	1.00	5.00	1.28
			632686	346.10	347.00	0.90	1.24	7.78	1.00	220.00	0.16
			632687	347.00	347.20	0.20	0.11	1.04	1.00	30.00	0.11
- CALCAREOUS MUDSTONE FACIES: Consists of grey to greyish black monotonous, calcareous siliceous carbonaceous mudstone. There are no feathery calcite beds or pyrite-calcite blebs in the facies, making it easily distinguishable from the CCMS.			632688	347.20	347.40	0.20	18.41	3.83	4.00	110.00	4.81
			632689	347.40	347.80	0.40	1.00	2.61	1.00	90.00	0.38
			632690	347.80	349.00	1.20	0.36	0.74	1.00	30.00	0.49
			632691	347.80	349.00	1.20	0.39	0.83	1.00	30.00	0.47
- GRADED LIMESTONE FACIES: Is a laminated argillaceous limestone with intercalated carbonaceous limestone laminae. The main rock type in the facies is laminated limestone with laminae up to 0.1-7mm thick.			632692	349.00	350.50	1.50	0.35	0.40	1.00	10.00	0.88
			632693	350.50	351.20	0.70	1.16	2.25	1.00	80.00	0.52
			632694	351.20	352.70	1.50	0.14	0.59	1.00	20.00	0.24
			632695	352.70	353.60	0.90	1.12	4.55	1.00	150.00	0.25
- LIGHT GREY BASAL LIMESTONE FACIES - LGLS: Consists of laminated argillaceous limestone. In the Anniv area it marks the end of the ACTM. It's not always present in the stratigraphy.			632696	353.60	354.70	1.10	0.45	0.94	1.00	30.00	0.48
			632697	354.70	356.30	1.60	0.95	2.14	1.00	80.00	0.44
			632698	356.30	357.20	0.90	0.55	0.83	1.00	30.00	0.66
			632699	357.20	357.40	0.20	3.36	13.13	4.00	370.00	0.26
- BASAL FACIES: This is a highly contorted and locally foliated carbonaceous mudstone. Unlike the other facies it is not repeated higher in the member. It appears locally to contain the slip zone of a major slump. The facies has only been observed in the YX area. It is 0.1-2m thick. The facies consists of massive carbonaceous siliceous mudstone with lenses and laminae of contorted,			632700	357.40	357.40	0.00	0.01	0.01	1.00	5.00	2.00
			632701	357.40	358.10	0.70	1.18	1.12	1.00	40.00	1.05
			632702	358.10	359.10	1.00	4.30	13.56	4.00	430.00	0.32
			632703	359.10	359.40	0.30	3.36	7.35	3.00	230.00	0.46
			632704	359.40	361.20	1.80	2.19	4.67	1.00	160.00	0.47
			632705	361.20	361.60	0.40	0.47	3.71	1.00	120.00	0.13
			632706	361.60	363.00	1.40	0.93	3.25	1.00	100.00	0.29
			632707	363.00	364.00	1.00	1.49	6.32	2.00	190.00	0.24
			632708	364.00	364.60	0.60	1.39	2.81	1.00	80.00	0.49

Selwyn Project Diamond Drill Log

Hole Number:
XYC-206

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		<i>slightly carbonaceous chert.</i>	632709	364.60	364.90	0.30	1.36	0.43	1.00	10.00	3.16
		-----	632710	364.90	364.90	0.00	0.91	1.34	222.00	90.00	0.68
		« 324.20- 324.70 Siliceous carbonaceous finely laminated mudstone with some sphalerite. Black. Sph»	632711	364.90	366.40	1.50	1.52	4.38	1.00	110.00	0.35
			632712	366.40	368.00	1.60	1.21	2.69	1.00	90.00	0.45
		« 324.70- 324.80 Light grey limestone. No mineralization. »	632713	368.00	369.50	1.50	2.30	6.94	3.00	200.00	0.33
			632714	369.50	371.00	1.50	0.76	2.96	1.00	80.00	0.26
			632715	371.00	372.70	1.70	0.76	0.53	1.00	20.00	1.43
		« 324.80- 325.00 Siliceous, finely laminated mustone with some sphalerite. Good grade. Sph »	632716	372.70	374.70	2.00	0.45	0.47	1.00	20.00	0.96
			632717	374.70	376.20	1.50	0.23	0.07	1.00	5.00	3.29
			632718	376.20	377.70	1.50	0.41	1.20	1.00	40.00	0.34
		« 325.00- 325.30 Limestone. Slightly carbonaceous. Finely laminated. No visible mineralization. »	632719	377.70	379.10	1.40	0.87	5.62	1.00	180.00	0.15
			632720	379.10	382.20	3.10	2.30	4.72	1.00	200.00	0.49
			632721	379.10	382.20	3.10	1.80	4.27	1.00	160.00	0.42
		« 625.30- 326.10 Silicified, finely laminated mudstone with moderate amount of sphalerite visible. »	632722	382.20	383.20	1.00	0.24	0.60	1.00	20.00	0.40
			632723	383.20	384.30	1.10	3.82	6.79	1.00	280.00	0.56
			632724	384.30	385.50	1.20	10.46	14.36	3.00	690.00	0.73
		« 326.10- 326.70 Limestone. Laminated. Somewhat carbonaceous. Light to medium grey. No visible mineralization. »	632725	385.50	386.50	1.00	9.39	15.08	3.00	660.00	0.62
			632726	386.50	387.50	1.00	14.02	19.61	3.00	990.00	0.71
			632727	387.50	388.50	1.00	12.72	14.16	3.00	790.00	0.90
		« 326.70- 328.60 Siliceous, carbonaceous mudstone with fine cherty laminae. Moderate mineralization; sphalerite in laminae. Calcite veining throughout. Graded limesto ne concretions less than 10 cm wide No visible mineralization. »	632728	388.50	389.50	1.00	11.49	14.81	2.00	780.00	0.78
			632729	389.50	390.30	0.80	14.93	19.29	4.00	1000.00	0.77
			632730	390.30	390.30	0.00	0.12	0.11	1.00	5.00	1.09
			632731	390.30	391.00	0.70	14.40	21.65	5.00	1020.00	0.67
			632732	391.00	391.60	0.60	6.71	9.48	3.00	430.00	0.71
		« 328.60- 330.60 Carbonaceous, highly calcareous mudstone with thick cherty banding. Black to light grey. One 4 cm band of sphalerite laminae at 329.1 m. No mineralization other than that. »	632733	391.60	392.60	1.00	1.82	8.59	2.00	260.00	0.21
			632734	392.60	394.10	1.50	0.32	0.25	1.00	5.00	1.28
			632735	394.10	396.60	2.50	0.18	0.71	1.00	20.00	0.25
			632736	396.60	397.60	1.00	6.50	14.78	5.00	480.00	0.44
		« 330.60- 331.60 Monotonous siliceous/cherty mudstone. Varies from light to dark grey with miniscule calcite stringers. No visible mineralization. »	632737	397.60	399.70	2.10	12.82	17.75	8.00	570.00	0.72
			632738	399.70	401.70	2.00	0.06	0.03	1.00	5.00	2.00
			632739	401.70	402.70	1.00	0.03	0.05	1.00	5.00	0.60
		« 331.60- 332.50 Calcareous carbonaceous mudstone with miniscule calcite veins. »	632740	402.70	402.70	0.00	1.42	4.42	25.00	280.00	0.32
			632741	402.70	404.80	2.10	0.45	0.11	1.00	5.00	4.09
			632742	404.80	406.00	1.20	0.39	0.39	1.00	10.00	1.00
		« 323.50- 334.50 Monotonous siliceous mudstone. Carbonaceous. »	632743	406.00	407.00	1.00	0.12	1.04	2.00	30.00	0.12

Selwyn Project Diamond Drill Log

Hole Number:
XYC-206

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
« 334.50- 334.90 Limestone. Medium grey, bedded. No visible mineralization. » « 334.90- 337.80 Laminated silicified carbonaceous mudstone. Black. Sphalerite in laminae. » « 335.10- 336.80 FLT »« brco 10%»« flt bx 90%» « 337.80- 340.50 Laminated carbonaceous mudstone. Trace sphalerite visible in laminae. » « 340.50- 340.70 Limestone. Graded, medium grey, trace sphalerite possible. » « 340.70- 343.10 Monotonous siliceous carbonaceous mudstone. Abundant stylolites. No visible mineralization. » « 343.10- 344.30 Laminated siliceous mudstone. Black. Sphalerite associated with well developed laminae; laminae are warped and folded. Traces of galena also visible. Mineralization visible: 5-10% combined. Two small (2-3 cm) limestone concretions with pyrite nearby. Some small blebs of galena are visible. Lower 30 cm of section is weakly calcareous. » « 344.30- 346.10 Laminated limestone. No visible mineralization. » « 346.10- 347.00 Laminated carbonaceous calcareous mudstone. Black with easily visible laminae defined by sphalerite. » « 347.00- 347.20 Limestone. Graded, light grey, weakly laminated. No visible mineralization. » « 347.20- 347.40 Laminated siliceous mudstone. Coarse galena and fine sphalerite are visible. »			632744	407.00	408.00	1.00	0.19	0.26	1.00	5.00	0.73
			632745	408.00	409.00	1.00	0.11	1.30	1.00	40.00	0.08
			632746	409.00	410.50	1.50	0.15	0.75	2.00	20.00	0.20
			632747	410.50	412.00	1.50	0.03	0.30	1.00	5.00	0.10
			632748	412.00	413.60	1.60	0.07	0.62	1.00	20.00	0.11
			632749	413.60	415.10	1.50	0.26	3.06	6.00	80.00	0.08
			632750	415.10	416.60	1.50	0.08	0.55	3.00	20.00	0.15
			632751	415.10	416.60	1.50	0.29	2.69	6.00	70.00	0.11
			632752	416.60	418.30	1.70	0.54	0.27	4.00	5.00	2.00
			632753	418.30	419.80	1.50	0.01	0.01	1.00	5.00	2.00
			632754	419.80	421.30	1.50	0.01	0.01	1.00	5.00	2.00

Selwyn Project

Diamond Drill Log

Hole Number:
XYC-206

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		« 347.40- 347.80 Laminated limestone. Light grey. Galena and sphalerite are visible in the laminae. »									
		« 347.80- 352.70 Black calcareous mudstone. Monotonous except for some pyrite blebs. No visible mineralization. »									
		« 352.70- 357.20 Limestone. Veins of calcite on mm-scale with associated pyrite. Weakly laminated with sphalerite. Light grey. Some time mudstone occurring in laminae darkens the section. »									
		« 357.20- 372.70 Mixed section containing intercalated limestone and laminated calcareous mudstone. Sphalerite occurs in laminated sections. »									
		« 359.10- 359.40 Fault with slick n slides present. Core lost. FLT »« brco 85%»« flt bx 10%»« flt gg 5%»									
		« 360.30- 361.60 Fault with slick n slides present. Core lost. FLT »« brco 20%»« flt bx 75%»« flt gg 5%»									
		« 372.70- 374.70 Massive to weakly graded limestone. Medium grey. Trace sphalerite? »									
		« 374.70- 383.20 Dark grey weakly laminated limestone. Infrequent wormy calcite veins. Trace sphalerite? »									
		« 378.80- 382.60 Fault. Poor recovery. FLT »« brco 40%»« flt bx 50%»« flt gg 10%»									
		« 383.20- 391.00 Calcareous laminated mudstone. High grade mineralization of galena and sphalerite. Light grey. »									
		« 391.00- 391.60 Carbonaceous limestone, medium to dark grey. No visible mineralization. »									
		« 391.60- 402.70 Siliceous mudstone with laminae and limestone									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-206

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		concretions. Some sphalerite in laminae. » « 394.10- 397.60 FLT »« brco 10%»« flt bx 70%»« flt gg 20%» « 398.20- 399.60 Crumbled. Core lost, poor recovery. FLT »« flt bx 10%»« flt gg 90%» « 402.80- 413.60 Dark grey to black carbonaceous limestone. Mostly massive with occasional faint laminae. Calcite veining sub-parallel TCA, veins are mm to cm scale. Occasional pyrite associated with calcite veins. Trace sphalerite. » « 403.10- 404.80 Fault. Slick n slides present. FLT »« flt bx 70%»« flt gg 30%» « 413.60- 418.30 Siliceous mudstone with minor mineralization. Black. » « 418.30- 427.20 Basal limestone. Light grey, laminated. Bedding at 20 TCA. No mineralization. »									
427.20	445.40	CCMS CCMS – Calcareous Mudstone Massive, calcareous, carbonaceous, dark grey mudstone. Most of the member is massive, but rare poorly defined bedding and pyrite-calcite micro-concretions are present. Most diagnostic structures are feathery calcite beds (=thin calcite-cemented concretions, many of them contain pyrite cores) and calcite pseudo-beds (= fibrous calcite vein parallel to bedding). « lm ca 5.00-10.00mm », « nodules py -3.00% 2.00-20.00mm », Dark grey to black mudstone, occasionally weakly graded. Siliceous, with									



Hole Number:
XYC-206

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
calcite veining.											
445.40	445.40	EOH									

Diamond Drill Log

Comprehensive Report for Hole:

XYC-205

Hole No.: XYC-205	Depth: 416.10 m	Horizontal Length: 0.00 m	Project: 1710
Location Data:			
Property:	Selwyn Project	Claim Name:	X 2
Mining District:	Selwyn Basin	Grant Number:	Y 64527
Province/Territory:	Yukon		
UTM Co-Ordinates & Altitude of Drill Hole Collar:			
UTM Easting:	488416.00 m	True Azimuth:	25.0 °
UTM Northing:	6926726.00 m	Hole Angle:	-85.0 °
Elevation (m):	1585.00 m	NTS Name:	Placer Creek
		NTS Number:	105I06
Grid Co-Ordinates of Drill Hole Collar:			
Grid Easting (m):	0.00 m	Grid Name:	HP 06
Grid Northing (m):	0.00 m	Grid Type:	100m
Grid Azimuth:	85.0 °		
Dimond Drilling Contract:			
Drilled By:	NL-02	Date Drilling Start:	09/01/2010
		Date Finish:	09/08/2010
Diamond Drill Core:			
Logged By:	Matthew Jodrey / Kate	Date Logging Start:	09/09/2010
		Date Finish:	09/17/2010
Legend for Core Logging Codes: PAX			
Core Size:	NQ3	Cemented:	Yes
Casing Depth:	10.40 m	Casing Pulled:	Yes
Water Depth:	0.00 m	Overburden Depth:	10.40 m
Level:	Section:	Drift:	

Selwyn Project

Diamond Drill Log

Survey Data for Hole

XYC-205

Hole Comments:

Thu, Sep 02 --- The drill got moved yesterday morning. During dayshift 35' of casing got drilled. Night shift started coring and drilled to a total depth of 41.1m, all BSSM.

=====

Fri, Sep 03 --- The nightshift drove their truck in the ditch at XY this morning. It rained all night which made one particular stretch on the road really bad. When driving up a hill just leaving the drill, it turned out they couldn't make it all the way to the top, so they backed up gently, they hit the breaks once and the truck started sliding and ended up in the ditch. Nobody got hurt and there was no damage to the truck. Dale suggested to his drillers to use his Teryx for that last slippery part of the road to the drill. At morning shift change the total depth was 119.1m, in BSSM. A fault was encountered from 90m to 99m. Locally bioturbated stretches visible.

=====

Sat, Sep 04 --- Right now in FLMD at a total depth of 161.1m. Core is competent and no mechanical problems to mention.

=====

Sun, Sep 05 --- In FLMD at a total depth of 213.1m. Core is competent, no mechanical problems to mention. Darcy trained night shift on the devicore last night.

=====

Mon, Sep 06 --- In USMS at a total depth of 297m. Core is competent, locally broken up with some minor fault gauge.

=====

Tue, Sep 07 --- In ACTM at a total depth 363.1m. The ACTM interval started at a depth of approximately 350m. The core is rather competent, with locally some broken core and minor fault breccia.

=====

Wed, Sep 08 --- ACTM was intersected between 350m and 402.2m. The hole is right now at 416.1m in CCMS. A fault was intersected from 402.2m to 408.1m and another fault from 414m to 416.1m. The rods broke apart, luckily only 3m down the hole. The hole got shut down this morning after discussing with JJ, as we only had 14m of footwall rock. The drill will get 'moved' to target #32, which is on the same setup (coordinates got changed a few days ago).

<i>Depth</i>	<i>Dip</i>	<i>Azimuth</i>
0.00	-85.0	25.0
50.00	-84.0	30.4
100.00	-84.4	35.6
150.00	-83.8	51.2
200.00	-84.5	50.0
249.10	-84.7	64.8
300.10	-84.4	64.6
350.00	-85.7	67.2
401.00	-85.1	77.4

Selwyn Project Diamond Drill Log

Hole Number:
XYC-205

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
0.00	10.40	OVBR									
10.40	105.80	BSSM									
<i>BSSM – Backside Siliceous Mudstone</i> <i>Devonian Siliceous Mudstone – Upper Chert Formation</i> <i>Greyish black laminated chert and siliceous mudstone. Randomly-oriented to bedding-parallel bioturbation is common in the bottom of the unit. « lm chrt 75.00-95.00% », « btrb 0.10-2.00cm »,</i> <i>Very fractured and broken up throughout unit « broken 60%» « bx 15%»« gouge 1%» throughout unit). Generally typical lithology, med-dk grey mdst, not strongly calcareous, includes sections of bioturbation, some concretions.</i> <i>< @ 17.40 faint planar parallel pyrite nodules, like PSMS S0 tca 40% ></i> <i>« 19.80- 29.60 flt zone »« bx 30%»« gouge 2%»« broken 65%»</i> <i>< @ 29.90 calcite rich laminations S0 tca 57° ></i> <i>< @ 37.30 calcite rich laminations s0 tca 58° ></i> <i>< @ 37.90 first appearance bioturbations ></i> <i>« 47.70- 52.00 flt zone »« flt bx 30%»« flt gg 10%»« broken 60%»</i> <i>« 52.00- 64.80 Light grey, siliceous, bioturbated range bioturb »</i> <i>« 53.30- 57.00 flt »</i> <i>« 55.30- 57.00 flt bx 50%»« flt gg 15%»« brco 35%»</i> <i>« 56.20- 56.60 hydrozincite mineralization on fracture surfaces »</i>											

Selwyn Project Diamond Drill Log

Hole Number:
XYC-205

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		◁ @ 57.10 Bedding in parallel carbonaceous beds S0 TCA 52° ▷ ◁ @ 60.20 Bedding in parallel carbonaceous beds S0 TCA 50° ▷ ◁ 65.90- 73.10 Fault zone. FLT ▷◁ flt bx 30%▷◁ flt gg 10%▷◁ brco 50%▷ ◁ 76.30- 78.60 Fault zone FLT ▷◁ flt bx 30%▷◁ flt gg 30%▷◁ brco 40%▷ ◁ @ 82.30 Bedding in cherty parallel planar laminations S0 TCA 45° ▷ ◁ @ 87.30 Bedding in carbon rich laminations, varies locally somewhat S0 TCA 46° ▷ ◁ 90.20- 98.80 Major Fault FLT ▷◁ flt bx 60%▷◁ flt gg 10%▷◁ brco 30%▷ ◁ @ 102.30 Bedding in a limestone bed. Note that this is NOT a concretion. S0 TCA 47° ▷									
105.80	235.90	FLMD									
		FLMD – Flaggy Mudstone Formation Dark grey mudstone in the upper portions of the unit grading into light grey mudstone to siltstone. Contains abundant wispy bioturbation which ranges from randomly-oriented at the top of the unit to bedding-parallel throughout the majority of the unit. Darker upper section has a strong fetid odour along broken surfaces. ◁ btrb 0.10-2.00cm ▷, ◁ cg xtl crns ca 1.00-5.00% 5.00-150.00cm ▷, ◁ crns py 1.00-5.00% 0.10-0.50mm ▷, As per unit description. ◁ 105.80- 125.90 Very broken zone ▷ ◁ 107.10- 110.10 Fault zone. FLT ▷◁ flt bx 28%▷◁ flt gg 2%▷◁ brco 70%▷									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-205

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
« 110.90- 113.70 Fault zone. FLT »« flt bx 50%»« flt gg 3%»« brco 40%»											
◁ @ 112.70 Bedding in calcite-pyrite rich bed S0 TCA 63° ▷											
« 114.70- 116.80 Fault zone. FLT »« flt bx 50%»« flt gg 5%»« brco 45%»											
◁ @ 130.80 Bedding in carbonaceous bed S0 TCA 60° ▷											
◁ @ 146.60 Bedding in carbonaceous bed S0 TCA 44° ▷											
« 166.20- 177.00 Dark-medium grey range; includes laminated limestone »											
◁ @ 168.80 Bedding in calcite rich laminations S0 TCA 55° ▷											
« 196.00- 196.30 Fault FLT »« flt bx 50%»« flt gg 30%»											
◁ @ 207.80 Bedding in carbonaceous bed S0 TCA 44° ▷											
◁ @ 228.90 Bedding in carbonaceous bed S0 TCA 35° ▷											
235.90	349.80	USMS	632201	269.70	269.90	0.20	0.27	6.79	6.00	210.00	0.04
USMS – Upper Siliceous Mudstone			632202	348.90	349.70	0.80	0.09	0.76	1.00	30.00	0.12
Consists of interlaminated dark grey to black mudstone and light to medium grey chert. Regionally, a 1m thick graptolite zone occurs 15m below the top of the upper unit, this is usable as a horizon. The USMS is divided into 3 units. The Lower Unit contains abundant limestone concretions and Galena and sphalerite micro-concretions occur locally near the base of this unit. « gra , lm chrt -20.00% », « cg xtl sph crns ca 5.00-20.00cm », « bed chrt 10.00-15.00% », Typical; as per unit description. ◁ @ 236.90 Bedding in calcite rich laminations S0 TCA 38° ▷											

Selwyn Project Diamond Drill Log

Hole Number:
XYC-205

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
< @ 240.50 Bedding in calcite rich laminations S0 TCA 35° > < @ 251.10 Bedding in parallel cherty beds S0 TCA 40° > « 264.10- 270.10 Broken zone; includes several small faults. » < @ 265.30 Bedding in parallel cherty beds S0 TCA 34° > « 265.60- 265.90 Fault FLT »« flt bx 30%»« flt gg 10%»« brco 60%» « 267.40- 269.40 Fault . FLT »« flt bx 20%»« flt gg 5%»« brco 60%» « 268.80- 270.10 Mineralized range. Calcareous mudstone. Laminated. Niton detected up to 8% Zn and 0.5% Pb » « 279.00- 291.50 Broken range » « 288.00- 289.60 Fault. FLT »« flt bx 30%»« flt gg 5%»« brco 65%» < @ 291.60 Bedding in parallel cherty beds S0 TCA 33° > < @ 303.40 Bedding in parallel cherty beds S0 TCA 47° > « 321.40- 322.00 Fault FLT »« flt bx 20%»« flt gg 5%»« brco 75%» < @ 323.40 Bedding in calcite-pyrite rich 1 cm bed S0 TCA 50° > < @ 331.00 Bedding in parallel cherty beds S0 TCA 35° > « 342.70- 343.80 Fault FLT »« flt bx 20%»« flt gg 5%»« brco 75%» « 349.10- 349.80 Fault FLT »« flt bx 35%»« flt gg 5%»« brco 65%»											
			632203	349.70	350.20	0.50	1.24	7.45	3.00	350.00	0.17

Selwyn Project Diamond Drill Log

Hole Number:
XYC-205

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
349.80	399.10	ACTM	632204	350.20	350.80	0.60	2.23	5.48	2.00	200.00	0.41
ACTM – Active Member			632205	350.80	351.20	0.40	1.07	7.11	2.00	210.00	0.15
The ACTM consists of a repetitive, possibly rhythmic, sequence of intercalated carbonaceous mudstone, cherty mudstone, chert and limestone and locally contains economically significant Zn and Pb sulphides (see bold marked facies), mainly in its sections with well developed lamination. Because of its heterogeneity, the member is distinctive and easily identified. ===== The ACTM has 8 different facies: ===== - GREY CHERT FACIES: Consists of laminated medium light grey to medium dark grey chert. Mineralization: 95-99% quartz and up to 5% secondary calcite. - WHITISH GREY ZN-PB MUDSTONE FACIES: Is a laminated cherty rock containing up to 70% sulphides. Mineralization: quartz, sphalerite and galena are the major minerals with only minor amounts of pyrite and locally calcite. Sedimentary diagenetic structures are common and well displayed in the facies, such as: lamination, pseudo-beds, calcite nodules & limestone nodules and abundant water escape structures. Most obvious structure in facies is cross-cutting veins containing massive sphalerite and galena with minor pyrite. They range in width from 0.5 to 10mm. - THIN BEDDED CHERTY MUDSTONE FACIES: Consists of rhythmic intercalated laminae of chert, carbonaceous mudstone and minor micrite. This facies contains significant amounts of Zn and Pb sulphides. - CHERTY MUDSTONE FACIES: Consists of a greyish black monotonous siliceous, carbonaceous mudstone. It is most typically found overlying the thin bedded calcareous mudstone facies. - THIN BEDDED CALCAREOUS MUDSTONE FACIES: Consists of laminated			632206	351.20	351.70	0.50	2.58	7.88	3.00	320.00	0.33
			632207	351.70	352.20	0.50	2.70	15.91	4.00	570.00	0.17
			632208	352.20	352.70	0.50	0.45	1.99	1.00	60.00	0.23
			632209	352.70	353.10	0.40	0.81	5.35	1.00	150.00	0.15
			632210	353.10	353.70	0.60	0.76	8.88	2.00	190.00	0.09
			632211	353.10	353.70	0.60	1.00	8.44	2.00	180.00	0.12
			632212	353.70	354.30	0.60	4.14	10.45	2.00	260.00	0.40
			632213	354.30	354.80	0.50	0.80	0.10	1.00	5.00	8.00
			632214	354.80	355.20	0.40	1.38	7.00	1.00	180.00	0.20
			632215	355.20	355.50	0.30	0.44	1.17	1.00	30.00	0.38
			632216	355.50	355.90	0.40	0.49	1.91	1.00	50.00	0.26
			632217	355.90	357.00	1.10	0.06	0.53	1.00	10.00	0.11
			632218	357.00	357.70	0.70	0.17	0.99	1.00	20.00	0.17
			632219	357.70	358.40	0.70	0.17	0.83	1.00	20.00	0.20
			632220	358.40	358.40	0.00	0.01	0.01	1.00	5.00	2.00
			632221	358.40	359.60	1.20	0.26	1.33	1.00	40.00	0.20
			632222	359.60	360.70	1.10	0.75	3.27	1.00	90.00	0.23
			632223	360.70	361.00	0.30	0.01	0.10	1.00	5.00	0.10
			632224	361.00	362.10	1.10	0.04	0.45	1.00	10.00	0.09
			632225	362.10	362.50	0.40	1.49	14.41	2.00	410.00	0.10
			632226	362.50	363.50	1.00	0.06	0.53	1.00	20.00	0.11
			632227	363.50	364.40	0.90	0.20	0.17	1.00	5.00	1.18
			632228	364.40	365.30	0.90	0.63	4.35	1.00	120.00	0.14
			632229	365.30	366.10	0.80	1.71	5.95	1.00	170.00	0.29
			632230	366.10	366.10	0.00	5.74	6.84	68.00	180.00	0.84
			632231	366.10	366.80	0.70	1.04	6.88	1.00	170.00	0.15
			632232	366.80	367.60	0.80	0.66	3.57	1.00	100.00	0.18
			632233	367.60	367.90	0.30	1.01	3.84	1.00	110.00	0.26
			632234	367.90	368.90	1.00	0.40	1.87	1.00	50.00	0.21
			632235	368.90	369.80	0.90	1.02	9.16	2.00	240.00	0.11
			632236	369.80	371.00	1.20	0.75	4.19	1.00	110.00	0.18
			632237	371.00	373.60	2.60	1.78	8.14	2.00	220.00	0.22

Selwyn Project Diamond Drill Log

Hole Number:
XYC-205

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
carbonaceous mudstone containing 20-40% calcite, 40-55% quartz and 10-20% muscovite. Sulphides occur in laminae. In the XY area it is usually the lowest facies in the section to contain laminated sulphides. - CALCAREOUS MUDSTONE FACIES: Consists of grey to greyish black monotonous, calcareous siliceous carbonaceous mudstone. There are no feathery calcite beds or pyrite-calcite blebs in the facies, making it easily distinguishable from the CCMS. - GRADED LIMESTONE FACIES: Is a laminated argillaceous limestone with intercalated carbonaceous limestone laminae. The main rock type in the facies is laminated limestone with laminae up to 0.1-7mm thick. - LIGHT GREY BASAL LIMESTONE FACIES - LGLS: Consists of laminated argillaceous limestone. In the Anniv area it marks the end of the ACTM. It's not always present in the stratigraphy. - BASAL FACIES: This is a highly contorted and locally foliated carbonaceous mudstone. Unlike the other facies it is not repeated higher in the member. It appears locally to contain the slip zone of a major slump. The facies has only been observed in the YX area. It is 0.1-2m thick. The facies consists of massive carbonaceous siliceous mudstone with lenses and laminae of contorted, slightly carbonaceous chert. ----- Generally very low grade; atypically competent; unusually rich in limestone beds/concretions. « 349.80- 350.30 Laminated siliceous mudstone. Moderate visible disseminated mineralization. » « 350.30- 350.80 Totally broken up laminated siliceous mudstone. Weak											
			632238	373.60	374.10	0.50	2.11	8.22	1.00	240.00	0.26
			632239	374.10	375.70	1.60	0.32	0.16	1.00	5.00	2.00
			632240	375.70	377.20	1.50	1.25	2.24	1.00	110.00	0.56
			632241	375.70	377.20	1.50	1.29	2.29	1.00	110.00	0.56
			632242	377.20	378.10	0.90	0.03	0.17	1.00	5.00	0.18
			632243	378.10	378.60	0.50	0.78	1.69	1.00	40.00	0.46
			632244	378.60	378.90	0.30	4.55	17.82	5.00	430.00	0.26
			632245	378.90	379.30	0.40	0.09	0.22	1.00	5.00	0.41
			632246	379.30	379.70	0.40	0.33	0.93	1.00	40.00	0.35
			632247	379.70	380.40	0.70	9.39	13.09	3.00	610.00	0.72
			632248	380.40	380.70	0.30	0.12	0.18	1.00	5.00	0.67
			632249	380.70	382.20	1.50	0.43	0.74	1.00	30.00	0.58
			632250	382.20	382.20	0.00	0.01	0.01	1.00	5.00	2.00
			632251	382.20	383.10	0.90	0.06	0.88	1.00	30.00	0.07
			632252	383.10	384.10	1.00	0.05	0.28	1.00	10.00	0.18
			632253	384.10	384.70	0.60	0.24	1.24	3.00	50.00	0.19
			632254	384.70	385.80	1.10	0.07	0.69	1.00	30.00	0.10
			632255	385.80	387.00	1.20	0.22	0.57	1.00	30.00	0.39
			632256	387.00	388.10	1.10	0.07	0.65	1.00	30.00	0.11
			632257	388.10	388.40	0.30	0.07	0.43	1.00	20.00	0.16
			632258	388.40	389.30	0.90	0.16	4.35	4.00	160.00	0.04
			632259	389.30	390.30	1.00	0.05	0.28	1.00	10.00	0.18
			632260	390.30	390.30	0.00	1.42	2.93	17.00	180.00	0.48
			632261	390.30	391.80	1.50	0.35	1.41	1.00	50.00	0.25
			632262	391.80	393.30	1.50	0.56	2.61	5.00	100.00	0.21
			632263	393.30	394.50	1.20	0.09	1.02	1.00	40.00	0.09
			632264	394.50	395.70	1.20	0.05	0.53	3.00	20.00	0.09
			632265	395.70	396.70	1.00	0.08	0.87	1.00	40.00	0.09
			632266	396.70	397.00	0.30	0.31	1.75	1.00	90.00	0.18
			632267	397.00	397.30	0.30	13.39	17.79	11.00	950.00	0.75
			632268	397.30	398.20	0.90	0.39	1.86	1.00	90.00	0.21
			632269	398.20	398.80	0.60	0.11	0.75	1.00	30.00	0.15
			632270	398.80	399.10	0.30	0.04	0.09	1.00	5.00	0.44

Selwyn Project

Diamond Drill Log

Hole Number:
XYC-205

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		visible mineralization. »	632271	398.80	399.10	0.30	0.03	0.12	1.00	5.00	0.25
		« 350.80- 351.20 Laminated calcareous mudstone with moderate mineralization disseminated throughout. »									
		« 351.20- 351.70 Siliceous laminated mudstone with moderate visible disseminated mineralization and abundant pyrite nodules. »									
		« 351.70- 352.80 Laminated calcareous mudstone with moderate visible mineralization disseminated in the laminae throughout. »									
		« 352.80- 353.20 Broken up laminated calcareous mudstone with weak visible mineralization. »									
		« 353.20- 354.30 Calcareous laminated mudstone with moderate visible mineralization of sphalerite in laminae. »									
		« 354.30- 354.90 Limestone. Massive, monotonous. No visible mineralization. »									
		« 354.90- 355.20 Siliceous laminated mudstone. Black. Weak sphalerite mineralization. »									
		« 355.20- 354.430 Limestone. Massive, dark grey, intercalated with black laminated mudstone. Calcite veins in mudstone. Trace sphalerite visible in laminae. »									
		« 354.30- 354.90 Limestone. Massive, monotonous. No visible mineralization. »									
		« 354.90- 355.20 Siliceous laminated mudstone. Black. Weakly mineralized (sphalerite). »									
		« 355.20- 354.40 Limestone. Massive, dark grey, intercalated with black									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-205

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		<i>laminated limestone with calcite veins. Sphalerite occurs in laminae. »</i> <i>« 354.40- 360.70 Calcareous laminated mudstone. Weak sphalerite mineralization. Trace of galena. »</i> <i>« 360.70- 361.00 Limestone. Graded, barren. No visible mineralization. »</i> <i>« 361.00- 362.10 Siliceous carbonaceous unlaminated mudstone with abundant calcite stringers. Trace sphalerite. »</i> <i>« 362.10- 362.50 Siliceous laminated mudstone. Visible sphalerite. Niton indicates 19.1% Zn and 4.5% Pb. »</i> <i>« 362.50- 364.40 Limestone. Weakly graded, some calcite veining. Trace mineralization. »</i> <i>« 364.40- 365.30 Siliceous unlaminated carbonaceous mudstone with minor limestone concretions (<10 cm wide). Minor sphalerite. »</i> <i>« 365.30- 366.10 Weakly laminated black mudstone with sphalerite in laminae and minor galena. »</i> <i>« 366.10- 366.80 Well laminated siliceous mudstone. Moderate to good visible sphalerite mineralization in laminae. Trace galena. »</i> <i>« 366.80- 369.80 Limestone. Laminated with carbonaceous material with moderate visible sphalerite. »</i> <i>« 369.80- 371.00 Siliceous carbonaceous mudstone with limestone laminae. Moderate visible sphalerite mineralization in laminae. Dark grey. Trace galena. »</i> <i>« 371.00- 374.10 Black to dark grey siliceous laminated mudstone. Some fine laminae with sphalerite. Lots of calcite veining. Trace galena. »</i>									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-205

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		« 374.10- 375.70 Limestone with intercalated mudstone. Trace sphalerite (and galena?) mineralization. »									
		« 375.70- 378.10 Laminated limestone with minor lighter limestone concretions. »									
		« 378.10- 379.30 Siliceous carbonaceous mudstone with limestone concretions. Laminae contain sphalerite. »									
		« 379.30- 379.70 Limestone. Graded, medium grey. No visible mineralization. »									
		« 379.70- 380.40 Mudstone. Calcareous, laminated. HIGHLY mineralized with sphalerite but no galena. Niton indicates 25% Zn. »									
		« 380.40- 380.70 Laminated limestone. No visible mineralization; Niton reads no mineralization. »									
		« 380.70- 382.20 Siliceous carbonaceous mudstone with weak laminae and abundant carbonate veins. Trace mineralization(?) »									
		« 382.20- 383.10 Slightly carbonaceous limestone with some lamination and trace sphalerite. »									
		« 383.10- 384.10 Limestone. Medium grey with weak laminae. No visible mineralization. »									
		« 384.10- 384.70 Calcareous mudstone with 1 cm thick folded calcite veins and weak lamination. Some sphalerite. »									
		« 384.70- 385.80 Graded/laminated limestone. Monotonous, dark grey. Becomes coarser and lighter grey near base of section. Trace sphalerite.»									
		« 385.80- 387.00 Calcareous mudstone with abundant folded calcite veins.									

Selwyn Project

Diamond Drill Log

Hole Number:
XYC-205

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		Possible trace mineralization. »									
		« 387.00- 388.10 Carbonaceous limestone with some laminae and possible trace sphalerite. »									
		« 388.10- 388.40 Siliceous carbonaceous mudstone. Dark grey. Sphalerite mineralization. »									
		« 388.40- 390.30 Limestone. Top 20 cm is a calcite vein. Limestone is graded and looks like several large concretions are growing into each other. »									
		« 390.30- 395.70 Calcareous mudstone with weak lamination in some zones. Visible sphalerite and galena mineralization. »									
		« 395.70- 396.70 Calcareous mudstone with weak lamination. Sphalerite and galena mineralization. »									
		« 396.70- 397.00 Siliceous laminated mudstone with calcite veins. Trace mineralization. »									
		« 397.00- 397.30 Light grey calcareous mudstone. High grade mineralization; sphalerite and galena. Niton reading is skewed by high % of Pb. »									
		« 397.30- 390.20 Calcareous carbonaceous mudstone with limestone concretions. Trace mineralization. »									
		« 398.20- 398.80 Siliceous laminated carbonaceous mudstone. Trace mineralization. »									
		« 398.80- 399.10 Basal limestone; weakly graded. No visible mineralization. »									
399.10	416.10	CCMS	632272	399.10	400.40	1.30	0.18	1.60	1.00	90.00	0.11
		CCMS – Calcareous Mudstone	632273	400.40	401.10	0.70	0.14	1.38	3.00	70.00	0.10

[illegible]

Diamond Drill Log

Comprehensive Report for Hole:

XYC-204

Hole No.: XYC-204	Depth: 442.30 m	Horizontal Length: 0.00 m	Project: 1710
Location Data:			
Property:	Selwyn Project	Claim Name:	X 13
Mining District:	Selwyn Basin	Grant Number:	Y 64538
Province/Territory:	Yukon		
UTM Co-Ordinates & Altitude of Drill Hole Collar:			
UTM Easting:	488951.41 m	True Azimuth:	30.0 °
UTM Northing:	6926565.36 m	Hole Angle:	-82.0 °
Elevation (m):	1687.71 m	NTS Name:	Placer Creek
		UTM Datum:	NAD 83
		UTM Grid Zone:	9
		NTS Number:	105I06
Grid Co-Ordinates of Drill Hole Collar:			
Grid Easting (m):	0.00 m	Grid Name:	HP 06
Grid Northing (m):	0.00 m	Grid Type:	100m
Grid Azimuth:	90.0 °		
Dimond Drilling Contract:			
Drilled By:	NL-03	Date Drilling Start:	08/28/2010
		Date Finish:	09/03/2010
Diamond Drill Core:			
Logged By:	Matthew Jodrey	Date Logging Start:	07/31/2010
		Date Finish:	07/31/2010
Legend for Core Logging Codes: PAX			
Core Size:	NQ/NQ3	Cemented:	Yes
Casing Depth:	11.30 m	Casing Pulled:	No
Water Depth:	0.00 m	Overburden Depth:	11.30 m
Level:	Section:	Drift:	

Selwyn Project

Diamond Drill Log

Survey Data for Hole

XYC-204

Hole Comments:

Sun, Aug 29 --- The drill was spun around yesterday morning. Since then they have drilled 100m, all BSSM. Competent core. No mechanical problems to mention.

=====

Mon, Aug 30 --- Drilling is going really well. In BSSM at a total depth of 228m. In the past 24hrs they drilled 128m. The beginning of the hole was pretty broken up, now in competent core.

=====

Tue, Aug 31 --- Still in BSSM at a total depth of 338m. Drilling is going really well and the core is competent.

=====

Wed, Sep 01 --- Still in BSSM at a total depth of 350.8m. Yesterday they spent the whole day pulling rods, moved the drill a few meters away, fixed the bank with the CAT, pulled the drill back into place and line it up over the collar. Night shift put the rods back down and encountered some problems before succesful drilling

=====

Thu, Sep 02 --- Still in BSSM at a total depth of 399m. Core is still competent. Locally bioturbations present in the core; bands of pyrite at an angle tca of 31deg.

=====

Fri, Sep 03 --- Still in BSSM at a total depth of 423m. The final 5m is broken up. Driller told me that the last 2m which is still in the box at the drill is more broken than the core that arrived in camp. The last 3m of core in camp is broken up, contains fault breccia. We could be entering the fault. The plan is to drill through the fault, if the core gets competent again in the next few meters and it turned out not to be the fault we're looking for, we will shut down the hole.

=====

Sat, Sep 04 --- Finished the hole at a depth of 442m in BSSM. Missed target, in other panel. No ACTM at target depth, and no fault was intersected.

<i>Depth</i>	<i>Dip</i>	<i>Azimuth</i>
0.00	-82.0	30.0
46.00	-82.0	30.9
100.00	-81.7	35.1
139.60	-81.4	34.2
185.30	-81.5	35.5
276.80	-81.0	38.7
320.00	-80.8	33.8
368.50	-80.8	46.5
411.80	-80.5	50.0

Selwyn Project Diamond Drill Log

Hole Number:
XYC-204

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
0.00	11.90	OVBR									
11.90	442.30	BSSM									
BSSM – Backside Siliceous Mudstone											
Devonian Siliceous Mudstone – Upper Chert Formation											
Greyish black laminated chert and siliceous mudstone. Randomly-oriented to bedding-parallel bioturbation is common in the bottom of the unit. « lm chrt 75.00-95.00% », « btrb 0.10-2.00cm »,											
« 11.90- 20.90 broken; includes some flt breccia within range »											
« 20.90- 22.20 carbonaceous fault »« flt breccia 40%»« flt gouge 30%»											
« 22.20- 29.20 broken »											
◁ @ 24.50 fine grained pyrite beds (like PSMS) s0 tca 33° ▷											
« 29.20- 30.30 carbonaceous fault »« flt breccia 30%»« flt gouge 20%»											
◁ @ 30.80 calcite rich 1 cm beds s0 tca 32° ▷											
◁ @ 45.70 calcite-rich laminations s0 tca 32° ▷											
◁ @ 55.80 laminations defined by alternating calcite content (calcite-rich laminations) s0 tca 20° ▷											
« 64.80- 65.20 carbonaceous fault »« flt breccia 70%»« flt gouge 15%»											
◁ @ 73.00 calcite-rich laminations s0 tca 12° ▷											
◁ @ 88.50 calcite-rich laminations s0 tca 28° ▷											
◁ @ 96.40 calcite-rich laminations s0 tca 21° ▷											

Selwyn Project Diamond Drill Log

Hole Number:
XYC-204

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
< @ 107.00 calcite rich laminations s0 tca 30° > « 109.30- 113.00 fault» « flt breccia 60%»« flt gouge 5%» « 117.00- 131.30 very broken; includes 15 % flt breccia; 1% flt gouge »											
< @ 122.50 carbonaceous bed s0 tca 12° > « 131.30- 182.50 low bedding to core angle fault »« flt breccia 45%»« flt gouge 10%»« broken 35%»											
< @ 144.40 first appearance of bioturbations >											
< @ 160.70 carbonaceous laminations s0 tca 2° >											
< @ 184.30 carbonaceous laminations s0 tca 11° >											
< @ 189.40 carbonaceous laminations s0 tca 20° >											
< @ 192.80 carbonaceous laminations s0 tca 1° >											
< @ 205.40 carbonaceous bed s0 tca 24° >											
< @ 213.70 calcite-rich laminations s0 tca 42° >											
< @ 226.00 calcite-rich laminations s0 tca 40° >											
< @ 238.50 laminations in limestone bed s0 tca 44° >											
« 240.10- 300.50 competent, medium to dark grey mudstone; weakly, locally bioturbated with ameboid pyrite nodules throughout (as in flaggy mudstone) »											
< @ 302.50 carbonaceous laminations s0 tca 33° >											

Selwyn Project Diamond Drill Log

Hole Number:
XYC-204

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		< @ 313.00 Calcite-rich laminations S0 tca 30° > « 321.30- 327.30 Bioturbated; includes 4m of light grey bioturbated limestone (ie not a concretion). » < @ 327.40 Carbonaceous laminations. S0 tca 24° > « 337.80- 339.20 Flt »« Flt gg 2%» « Flt bx 30%»« Brco 67%» < @ 342.70 Calcite-rich laminations. S0 tca 20° > < @ 342.70 Beta 285° > < @ 350.20 Calcite-rich laminations. S0 tca 23° > < @ 350.20 Beta 285° > « 352.10- 353.10 Flt »« Flt bx 60%»« Brco 40%» < @ 363.40 Carbonaceous laminations. S0 tca 27° > < @ 376.60 Lenticular, parallel pyrite concretions. S0 tca 32° > < @ 391.90 Lenticular, parallel pyrite concretions. S0 tca 33° > < @ 403.80 Calcite-rich laminations. S0 tca 24° > < @ 415.80 Calcite-rich laminations. S0 tca 27° > « 418.50- 423.10 Flt »« Flt gg 2%»« Flt bx 28%»« Brco 60%» < @ 427.40 Calcite-rich laminations. S0 tca 24° > < @ 440.30 Carbonaceous bed. S0 tca 29° >									
442.30	442.30	EOH									

Diamond Drill Log

Comprehensive Report for Hole:

XYC-203

Hole No.: XYC-203	Depth: 399.70 m	Horizontal Length: 0.00 m	Project: 1710
Location Data:			
Property:	Selwyn Project	Claim Name:	X 15
Mining District:	Selwyn Basin	Grant Number:	Y 64540
Province/Territory:	Yukon		
UTM Co-Ordinates & Altitude of Drill Hole Collar:			
UTM Easting:	489069.80 m	True Azimuth:	210.0 °
UTM Northing:	6926570.31 m	Hole Angle:	-77.0 °
Elevation (m):	1700.67 m	NTS Name:	Placer Creek
		NTS Number:	105I06
Grid Co-Ordinates of Drill Hole Collar:			
Grid Easting (m):	0.00 m	Grid Name:	HP 06
Grid Northing (m):	0.00 m	Grid Type:	100m
Grid Azimuth:	270.0 °		
Dimond Drilling Contract:			
Drilled By:	NL-02	Date Drilling Start:	08/24/2010
		Date Finish:	09/01/2010
Diamond Drill Core:			
Logged By:	Jelle De Bruyckere	Date Logging Start:	08/30/2010
		Date Finish:	09/05/2010
Legend for Core Logging Codes: PAX			
Core Size:	NQ3	Cemented:	Yes
Casing Depth:	9.50 m	Casing Pulled:	Yes
Water Depth:	0.00 m	Overburden Depth:	9.50 m
Level:	Section:	Drift:	

Selwyn Project

Diamond Drill Log

Survey Data for Hole

XYC-203

Hole Comments:

Wed, Aug 25 --- Moved to set-up, 30 feet of casing lost return in casing, water problems at the drill last night, they think they are in bedrock
=====

Thu, Aug 26 ---In BSSM at a total depth of 65m. The core is rather competent and drilling is going well.
=====

Fri, Aug 27 --- Still in BSSM at a total depth of 146.5m. The core is competent and shows faint local bioturbations.
=====

Sat, Aug 28 --- Still in BSSM at a total depth of 209.5m. Competent core. No mechanical problems to mention.
=====

Sun, Aug 29 --- Still in BSSM at a total depth of 260.5m. Competent core. It seems that there is a bent rod somewhere in the hole which makes it hard to get the inner tube down the hole. In the final hours of the night shift, the inner tube got stuck in the rod string. The driller decided to release it and start pulling rods, in an attempt to locate the bent rod. While pulling rods, it turned out that the inner tube already fell down to the core barrel.
=====

Mon, Aug 30 --- After drilling another 57m in the past 24hrs, still in BSSM at a total depth of 317.5m at morning shift change. The core is less competent now, fairly broken up. From 301.0m to 302.5m 100% flt gg.
=====

Tue, Aug 31 --- At a depth of 358m at morning shift change. Right now in a fault that started at 350.5m. ACTM started roughly at 332m. From 332m to 333 we probably have the best mineralization (10cm of 22% combined and another 90cm of 5-6% combined). More visible mineralization from 346.5m to 348.7m (6-7% combined).
=====

Wed, Sep 01 --- The hole got shut down yesterday evening in CCMS at a total depth of 399.7m. The hole was cemented from 295m to EOH. The ACTM was intersected from 327.1m (exact) to 358m (approx, based on how it will be logged. There seems to be Basal Light Grey Limestone from 368.4m to 369.9m, with 357.8m-368.4 being barren broken up ACTM??). NL-02 will get moved to target #28 this morning.

<i>Depth</i>	<i>Dip</i>	<i>Azimuth</i>
0.00	-77.0	210.0
47.50	-77.0	213.6
98.00	-76.7	209.6
146.50	-76.5	212.7
197.50	-76.1	212.3
249.00	-75.9	214.8
296.50	-75.2	215.9
348.70	-74.7	215.5
399.00	-73.7	221.3

Selwyn Project

Diamond Drill Log

Hole Number:
XYC-203

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
0.00	9.50	OVBR									
9.50	293.80	BSSM									
BSSM – Backside Siliceous Mudstone											
Devonian Siliceous Mudstone – Upper Chert Formation											
Greyish black laminated chert and siliceous mudstone. Randomly-oriented to bedding-parallel bioturbation is common in the bottom of the unit. « lm chrt 75.00-95.00% », « btrb 0.10-2.00cm »											
« 9.50- 19.20 Section with weathered and broken up core, consisting of limestone and calcareous mudstone. Three smaller sections of breccia, consisting of limestone clasts in a calcite cement. »											
« 19.20- 129.10 Calcareous mudstone with locally well developed bedding. No bioturbations are present. Faint pyrite beds define bedding usually. Limestone nodules are present. »											
< @ 32.70 S0 defined 1mm thick pyrite band S0 tca 36° >											
< @ 33.80 S0 defined by faint pyrite bed S0 tca 40° >											
< @ 38.90 S0 defined by faint pyrite bed S0 tca 23° >											
< @ 40.30 S0 defined by faint pyrite bed S0 tca 34° >											
< @ 55.50 S0 defined by faint pyrite bed S0 tca 51° >											
< @ 60.90 S0 defined by faint pyrite bed S0 tca 51° >											
< @ 62.30 S0 defined by faint pyrite bed S0 tca 40° >											
< @ 64.10 S0 defined by faint pyrite bed S0 tca 47° >											
< @ 74.00 S0 defined by faint pyrite bed S0 tca 46° >											
< @ 84.20 S0 defined by faint pyrite bed S0 tca 35° >											
< @ 99.50 S0 defined by faint pyrite bed S0 tca 34° >											
< @ 116.40 S0 defined by faint pyrite bed S0 tca 35° >											
< @ 116.80 S0 defined by faint pyrite bed S0 tca 35° >											
< @ 125.00 S0 defined by faint pyrite bed S0 tca 33° >											
« 129.10- 138.80 Siliceous dark grey mudstone with thick chert bands (up											

Selwyn Project Diamond Drill Log

Hole Number:
XYC-203

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		to 10mm thick) and no bioturbations. » « 138.80- 293.80 Siliceous mudstone with locally bioturbations. Pyrite nodules are present. » « @ 157.40 S0 defined by parallel bioturbations and pyrite beds S0 tca 50° » « @ 175.80 S0 defined by faint pyrite beds S0 tca 27° » « @ 187.80 S0 defined by faint pyrite beds S0 tca 34° » « @ 193.50 S0 defined by faint pyrite beds S0 tca 35° » « @ 205.80 S0 defined by faint pyrite beds S0 tca 49° » « @ 219.00 S0 defined by faint pyrite beds S0 tca 45° » « @ 233.50 S0 defined by faint pyrite beds S0 tca 33° » « @ 256.80 S0 defined by 2mm thick pyrite bands S0 tca 37° » « @ 269.10 S0 defined by 1-4mm thick pyrite bands S0 tca 46° »									
		293.80 316.90 FLT « Flt gg 6%»« Flt bx 12%»« Brco 52%» « 300.50- 300.90 Breccia of siliceous mudstone clasts, pyrite and quartz. Nicely developed reconsolidation. » « 300.90- 302.50 Flt gg 100%» « @ 307.60 A 5cm long & 3mm wide galena stringer. »									
		316.90 327.10 USMS	631451	325.30	326.20	0.90	0.04	0.39	2.00	20.00	0.10
		USMS – Upper Siliceous Mudstone	631452	326.20	327.10	0.90	0.01	0.43	1.00	20.00	0.02
		Consists of interlaminated dark grey to black mudstone and light to medium grey chert. Regionally, a 1m thick graptolite zone occurs 15m below the top of the upper unit, this is usable as a horizon. The USMS is divided into 3 units. The Lower Unit contains abundant limestone concretions and Galena and sphalerite micro-concretions occur locally near the base of this unit. « gra , lm chrt -20.00% », « cg xtl sph crns ca 5.00-20.00cm », « bed chrt 10.00-15.00% »									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-203

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
« 316.90- 327.00 Not the typical USMS. Siliceous mudstone with carbonate concretions, pyrite blebs, minor local pyrite banding, some calcite veins but without chert bands or squiggly quartz+calcite+pyrite bands. »											
327.10	370.40	ACTM	631453	327.10	328.20	1.10	0.02	0.51	1.00	30.00	0.04
ACTM – Active Member			631454	328.20	328.50	0.30	0.01	0.01	1.00	5.00	2.00
The ACTM consists of a repetitive, possibly rhythmic, sequence of intercalated carbonaceous mudstone, cherty mudstone, chert and limestone and locally contains economically significant Zn and Pb sulphides (see bold marked facies), mainly in its sections with well developed lamination. Because of its heterogeneity, the member is distinctive and easily identified. ===== The ACTM has 8 different facies: ===== - GREY CHERT FACIES: Consists of laminated medium light grey to medium dark grey chert. Mineralization: 95-99% quartz and up to 5% secondary calcite. - WHITISH GREY ZN-PB MUDSTONE FACIES: Is a laminated cherty rock containing up to 70% sulphides. Mineralization: quartz, sphalerite and galena are the major minerals with only minor amounts of pyrite and locally calcite. Sedimentary diagenetic structures are common and well displayed in the facies, such as: lamination, pseudo-beds, calcite nodules & limestone nodules and abundant water escape structures. Most obvious structure in facies is cross-cutting veins containing massive sphalerite and galena with minor pyrite. They range in width from 0.5 to 10mm. - THIN BEDDED CHERTY MUDSTONE FACIES: Consists of rhythmic intercalated laminae of chert, carbonaceous mudstone and minor micrite. This facies contains significant amounts of Zn and Pb sulphides.			631455	328.50	328.70	0.20	1.31	2.03	1.00	200.00	0.65
			631456	328.70	329.20	0.50	4.27	5.16	5.00	620.00	0.83
			631457	329.20	329.60	0.40	1.10	1.20	1.00	80.00	0.92
			631458	329.60	330.10	0.50	6.89	4.96	4.00	350.00	1.39
			631459	330.10	330.60	0.50	9.64	8.86	4.00	530.00	1.09
			631460	330.60	331.20	0.60	3.15	5.27	3.00	230.00	0.60
			631461	330.60	331.20	0.60	3.65	4.83	3.00	210.00	0.76
			631462	331.20	332.00	0.80	3.34	12.99	5.00	540.00	0.26
			631463	332.00	332.20	0.20	9.76	14.31	5.00	680.00	0.68
			631464	332.20	332.90	0.70	1.26	5.37	2.00	160.00	0.23
			631465	332.90	333.70	0.80	1.51	6.94	2.00	190.00	0.22
			631466	333.70	334.30	0.60	0.60	5.56	1.00	130.00	0.11
			631467	334.30	334.70	0.40	0.02	0.34	1.00	5.00	0.06
			631468	334.70	335.40	0.70	1.00	9.75	2.00	220.00	0.10
			631469	335.40	336.00	0.60	0.61	3.36	1.00	80.00	0.18
			631470	336.00	336.00	0.00	0.01	0.01	1.00	5.00	2.00
			631471	336.00	337.30	1.30	2.71	2.33	1.00	70.00	1.16
			631472	337.30	339.40	2.10	1.11	4.60	1.00	160.00	0.24
			631473	339.40	340.50	1.10	2.85	12.26	2.00	370.00	0.23
			631474	340.50	341.60	1.10	0.81	2.14	1.00	60.00	0.38
			631475	341.60	342.70	1.10	1.95	3.61	1.00	120.00	0.54
			631476	342.70	343.80	1.10	0.95	2.29	1.00	70.00	0.41
			631477	343.80	345.00	1.20	1.30	5.12	1.00	170.00	0.25
			631478	345.00	346.00	1.00	0.32	2.95	1.00	80.00	0.11
			631479	346.00	347.00	1.00	1.61	7.62	1.00	200.00	0.21
			631480	347.00	347.00	0.00	1.47	4.24	32.00	270.00	0.35

Selwyn Project Diamond Drill Log

Hole Number:
XYC-203

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
- CHERTY MUDSTONE FACIES: Consists of a greyish black monotonous siliceous, carbonaceous mudstone. It is most typically found overlying the thin bedded calcareous mudstone facies. - THIN BEDDED CALCAREOUS MUDSTONE FACIES: Consists of laminated carbonaceous mudstone containing 20-40% calcite, 40-55% quartz and 10-20% muscovite. Sulphides occur in laminae. In the XY area it is usually the lowest facies in the section to contain laminated sulphides. - CALCAREOUS MUDSTONE FACIES: Consists of grey to greyish black monotonous, calcareous siliceous carbonaceous mudstone. There are no feathery calcite beds or pyrite-calcite blebs in the facies, making it easily distinguishable from the CCMS. - GRADED LIMESTONE FACIES: Is a laminated argillaceous limestone with intercalated carbonaceous limestone laminae. The main rock type in the facies is laminated limestone with laminae up to 0.1-7mm thick. - LIGHT GREY BASAL LIMESTONE FACIES - LGLS: Consists of laminated argillaceous limestone. In the Anniv area it marks the end of the ACTM. It's not always present in the stratigraphy. - BASAL FACIES: This is a highly contorted and locally foliated carbonaceous mudstone. Unlike the other facies it is not repeated higher in the member. It appears locally to contain the slip zone of a major slump. The facies has only been observed in the YX area. It is 0.1-2m thick. The facies consists of massive carbonaceous siliceous mudstone with lenses and laminae of contorted, slightly carbonaceous chert. « 327.10- 328.20 Siliceous carbonaceous mudstone with locally calcareous bands and calcite veins. Mineralization: 0.8% Zn / 0.0% Pb. »			631481	347.00	348.00	1.00	0.40	2.01	1.00	50.00	0.20
			631482	348.00	349.10	1.10	1.23	5.31	1.00	140.00	0.23
			631483	349.10	350.00	0.90	2.62	5.99	1.00	160.00	0.44
			631484	350.00	351.00	1.00	0.76	1.16	1.00	40.00	0.66
			631485	351.00	352.60	1.60	0.15	0.02	1.00	5.00	7.50
			631486	352.60	353.30	0.70	0.39	0.01	1.00	5.00	78.00
			631487	353.30	354.70	1.40	0.11	0.60	1.00	20.00	0.18
			631488	354.70	357.10	2.40	0.42	0.41	1.00	10.00	1.02
			631489	357.10	358.60	1.50	0.09	0.29	1.00	10.00	0.31
			631490	358.60	358.90	0.30	0.10	0.24	1.00	10.00	0.42
			631491	358.60	358.90	0.30	0.09	0.22	1.00	10.00	0.41
			631492	358.90	359.70	0.80	0.09	0.19	1.00	5.00	0.47
			631493	359.70	360.70	1.00	0.04	0.13	1.00	5.00	0.31
			631494	360.70	360.90	0.20	0.23	0.71	3.00	30.00	0.32
			631495	360.90	362.10	1.20	0.06	0.07	1.00	5.00	0.86
			631496	362.10	363.10	1.00	0.21	0.16	1.00	5.00	1.31
			631497	363.10	364.20	1.10	0.06	0.33	1.00	10.00	0.18
			631498	364.20	365.20	1.00	0.24	0.27	2.00	5.00	0.89
			631499	365.20	366.20	1.00	0.12	1.18	1.00	40.00	0.10
			631500	366.20	366.20	0.00	0.01	0.01	1.00	5.00	2.00
			631501	366.20	367.30	1.10	0.06	0.64	1.00	20.00	0.09
			631502	367.30	367.80	0.50	3.11	0.94	15.00	30.00	3.31
			631503	367.80	369.10	1.30	0.19	0.03	1.00	5.00	6.33
			631504	369.10	370.20	1.10	0.03	0.01	1.00	5.00	6.00
			631505	370.20	370.40	0.20	0.01	0.01	1.00	5.00	2.00

Selwyn Project Diamond Drill Log

Hole Number:
XYC-203

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		« 328.20- 328.50 Carbonate concretion. Barren. »									
		« 328.50- 328.70 Minor mineralized carbonate concretion. »									
		« 328.70- 330.10 Mineralized carbonate concretion with alternating sections of high grade (!) and low to average grade. Niton gives exaggerated values of 20% Zn and 80% Pb for the high grade sections. Mineralization: 10% Zn & 25% Pb. No galena blebs or stringers visible. Minor sphalerite visible. »									
		« 330.10- 330.60 High grade siliceous mudstone. Rich in galena stringers and blebs. Moderately developed lamination. Mineralization 10% Zn & 18% Pb. Disseminated pyrite present throughout. »									
		« 330.60- 332.00 Mineralized siliceous mudstone. Mineralization: 7% Zn & 2.5% Pb. Fair amount of pyrite. Well developed lamination. »									
		« 332.00- 332.20 Whitish Grey Zn Pb Mudstone Facies. Mineralization 15% Zn & 13% Pb. »									
		« 332.20- 334.30 Mineralized siliceous mudstone with overall moderately deloped lamination. Mineralization 4% Zn & 1% Pb. Minor pyrite bands and a limestone clast. »									
		« 334.30- 334.70 Graded carbonate concretion. »									
		« 334.70- 335.40 Mineralized siliceous mudstone with well developed lamination. Mineralization 7% Zn & 2% Pb. »									
		« 335.40- 337.30 Poorly mineralized calcareous mudstone with limestone concretions. Mineralization 2% Zn & 1% Pb. One visible galena stringer. Poorly developed lamination. »									
		« 337.30- 349.10 Poorly mineralized calcareous mudstone with limestone concretions. Mineralization 2.7% Zn & 1.7% Pb. Broken up section. One									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-203

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		visible galena stringer, surrounded by some well developed lamination. » « 349.10- 350.00 Mineralized calcareous mudstone with a well developed lamination. Visible galena stringers. Mineralization 4% Zn & 1.5% Pb. » « 350.00- 367.80 Broken up locally poorly mineralized very calcareous mudstone without any lamination. Carbonate concretions present. » « 367.80- 370.40 Basal Light Grey Limestone »									
370.40	399.70	CCMS	631506	370.40	371.20	0.80	0.02	0.22	1.00	10.00	0.09
		CCMS – Calcareous Mudstone	631507	371.20	372.20	1.00	0.03	0.03	1.00	5.00	1.00
		Massive, calcareous, carbonaceous, dark grey mudstone. Most of the member is massive, but rare poorly defined bedding and pyrite-calcite micro-concretions are present. Most diagnostic structures are feathery calcite beds (=thin calcite-cemented concretions, many of them contain pyrite cores) and calcite pseudo-beds (= fibrous calcite vein parallel to bedding). « lm ca 5.00-10.00mm », « nodules py -3.00% 2.00-20.00mm » « 370.40- 370.40 Classic CCMS as per unit description » « @ 376.30 S0 defined by calcite pseudo bed S0 tca 35° »									
399.70	399.70	EOH									

Selwyn Project

Diamond Drill Log

Comprehensive Report for Hole:

XYC-202

Hole No.: XYC-202	Depth: 394.10 m	Horizontal Length: 0.00 m	Project: 1710
Location Data:			
Property:	Selwyn Project	Claim Name:	X 13
Mining District:	Selwyn Basin	Grant Number:	Y 64538
Province/Territory:	Yukon		
UTM Co-Ordinates & Altitude of Drill Hole Collar:			
UTM Easting:	488953.58 m	True Azimuth:	216.0 °
UTM Northing:	6926567.73 m	Hole Angle:	-71.0 °
Elevation (m):	1687.82 m	NTS Name:	Placer Creek
		NTS Number:	105I06
Grid Co-Ordinates of Drill Hole Collar:			
Grid Easting (m):	0.00 m	Grid Name:	HP 06
Grid Northing (m):	0.00 m	Grid Type:	100m
Grid Azimuth:	276.0 °		
Dimond Drilling Contract:			
Drilled By:	NL-03	Date Drilling Start:	08/21/2010
		Date Finish:	08/28/2010
Diamond Drill Core:			
Logged By:	Gabe Xue	Date Logging Start:	08/22/2010
		Date Finish:	08/29/2010
Legend for Core Logging Codes: PAX			
Core Size:	NQ	Cemented:	Yes
Casing Depth:	13.40 m	Casing Pulled:	Yes
Water Depth:	0.00 m	Overburden Depth:	13.40 m
Level:			
Section:		Drift:	

Selwyn Project

Diamond Drill Log

Survey Data for Hole

XYC-202

Hole Comments:

Sat, Aug 21 --- drill move to set-up in morning, too dark and no lights on dozer to move drill

=====

Sun, Aug 22 ---45 feet of casing, in BSSM

=====

Mon, Aug 23 --- Going good, still in BSSM

=====

Tue, Aug 24 ---BSSM

=====

Wed, Aug 25 --- Small fault and into USMS,

=====

Thu, Aug 26 ---Still in USMS at a total depth of 319m. Approximately 33m of USMS was drilled in the past 24hrs, approaching ACTM.

=====

Fri, Aug 27 --- ACTM was encountered at approximately 335m. At morning shift change still in ACTM at a depth of 346.9m. The intersection shows a couple of well mineralized stretches with a fair amount of visible galena blebs & stringers and bands of sphalerite.

=====

Sat, Aug 28 --- ACTM was intersected from 335m-358m. The drill got shut down yesterday evening and is right now ready for a 'drill move' to setup #12 (180degree swing on same location). Final depth of hole is at 394m in CCMS.

<i>Depth</i>	<i>Dip</i>	<i>Azimuth</i>
0.00	-71.0	216.0
48.20	-70.3	215.6
93.90	-69.7	211.3
139.60	-68.1	211.2
185.30	-67.3	211.1
231.00	-66.5	215.9
277.10	-66.5	218.0
331.00	-65.3	216.4
377.30	-64.4	218.6

Selwyn Project Diamond Drill Log

Hole Number:
XYC-202

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
0.00	13.40	OVBR									
13.40	85.70	BSSM									
<i>BSSM – Backside Siliceous Mudstone</i> <i>Devonian Siliceous Mudstone – Upper Chert Formation</i> <i>Greyish black laminated chert and siliceous mudstone. Randomly-oriented to bedding-parallel bioturbation is common in the bottom of the unit. « lm chrt 75.00-95.00% », « btrb 0.10-2.00cm »</i> <i>The whole section is calcareous with local siliceous sections; faint beds are defined by very fine grained pyrite + _ calcite.</i> <i>« 23.80- 26.80 Well developed quartz veining »</i> <i>< @ 24.40 S0 defined by faint py bands S0 tca 47° ></i> <i>< @ 37.50 S0 defined by faint py bands S0 tca 45° ></i> <i><@ 44.70 S0 defined by faind py bands S0 tca 45° ></i> <i>« 66.10- 72.40 Fault Zone with 60% of broken core »« flt gg 20%» « flt bx 20»</i>											
85.70	197.40	FLMD									
<i>FLMD – Flaggy Mudstone Formation</i> <i>Dark grey mudstone in the upper portions of the unit grading into light grey mudstone to siltstone. Contains abundant wispy bioturbation which ranges from randomly-oriented at the top of the unit to bedding-parallel throughout the majority of the unit. Darker upper section has a strong fetid odour along broken surfaces. « btrb 0.10-2.00cm », « cg xtl crns ca 1.00-5.00% 5.00-150.00cm », « crns py 1.00-5.00% 0.10-0.50mm »</i>											

Selwyn Project Diamond Drill Log

Hole Number:
XYC-202

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
The bands of boiturbation are convolute fairly and TCA varies from 30 to 70 degrees. « 168.70- 175.10 Fault zone with 70% of broken FLMD core »« flt gg 10%»« flt bx 20%»											
197.40	335.30	USMS	633501	334.40	335.00	0.60	0.05	0.38	1.00	10.00	0.13
USMS – Upper Siliceous Mudstone			633502	335.00	335.30	0.30	0.44	0.40	2.00	20.00	1.10
Consists of interlaminated dark grey to black mudstone and light to medium grey chert. Regionally, a 1m thick graptolite zone occurs 15m below the top of the upper unit, this is usable as a horizon. The USMS is divided into 3 units. The Lower Unit contains abundant limestone concretions and Galena and sphalerite micro-concretions occur locally near the base of this unit. « gra , lm chrt -20.00% », « cg xtl sph crns ca 5.00-20.00cm », « bed chrt 10.00-15.00% » The most of cherty bands are convolute fairly and TCA varies from 15 to 60 degrees. « 197.40- 253.10 Local calcite-rich section with faint py beds » « 232.80- 234.10 Fault zone with 80% of broken USMS core » « 253.10- 279.10 Lots of squiggly cherty bands, py bands and veins »											
335.30	357.80	ACTM	633503	335.30	336.00	0.70	6.89	6.31	6.00	370.00	1.09
ACTM – Active Member			633504	336.00	337.10	1.10	2.73	7.70	3.00	420.00	0.35
The ACTM consists of a repetitive, possibly rhythmic, sequence of intercalated carbonaceous mudstone, cherty mudstone, chert and limestone and locally contains economically significant Zn and Pb sulphides (see bold marked facies), mainly in its sections with well developed lamination. Because of its heterogeneity, the member is distinctive and easily identified. =====			633505	337.10	338.00	0.90	5.56	3.36	3.00	220.00	1.65
			633506	338.00	338.20	0.20	0.50	2.50	1.00	120.00	0.20
			633507	338.20	339.00	0.80	1.91	6.37	2.00	300.00	0.30
			633508	339.00	339.70	0.70	2.39	7.10	3.00	250.00	0.34
			633509	339.70	340.40	0.70	3.97	13.18	3.00	670.00	0.30
			633510	340.40	341.10	0.70	0.94	5.62	1.00	170.00	0.17
			633511	340.40	341.10	0.70	0.80	5.15	1.00	160.00	0.16
			633512	341.10	341.90	0.80	1.37	8.62	1.00	230.00	0.16

Selwyn Project Diamond Drill Log

Hole Number:
XYC-202

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
The ACTM has 8 different facies: =====			633513	341.90	343.20	1.30	0.14	0.72	1.00	20.00	0.19
			633514	343.20	343.50	0.30	3.41	6.35	1.00	190.00	0.54
			633515	343.50	344.00	0.50	0.25	1.18	1.00	40.00	0.21
- GREY CHERT FACIES: Consists of laminated medium light grey to medium dark grey chert. Mineralization: 95-99% quartz and up to 5% secondary calcite.			633516	344.00	345.50	1.50	0.50	0.96	1.00	30.00	0.52
			633517	345.50	346.90	1.40	1.39	4.24	1.00	120.00	0.33
			633518	346.90	347.80	0.90	0.82	5.42	1.00	160.00	0.15
- WHITISH GREY ZN-PB MUDSTONE FACIES: Is a laminated cherty rock containing up to 70% sulphides. Mineralization: quartz, sphalerite and galena are the major minerals with only minor amounts of pyrite and locally calcite. Sedimentary diagenetic structures are common and well displayed in the facies, such as: lamination, pseudo-beds, calcite nodules & limestone nodules and abundant water escape structures. Most obvious structure in facies is cross-cutting veins containing massive sphalerite and galena with minor pyrite. They range in width from 0.5 to 10mm.			633519	347.80	349.20	1.40	0.86	3.97	1.00	120.00	0.22
			633520	349.20	349.20	0.00	0.01	0.01	1.00	5.00	2.00
			633521	349.20	349.60	0.40	1.38	2.89	1.00	100.00	0.48
			633522	349.60	350.50	0.90	2.48	11.85	3.00	340.00	0.21
			633523	350.50	351.30	0.80	0.57	1.50	1.00	50.00	0.38
			633524	351.30	352.50	1.20	0.01	0.03	1.00	5.00	0.33
			633525	352.50	353.30	0.80	0.19	0.99	1.00	30.00	0.19
			633526	353.30	354.10	0.80	0.13	0.15	1.00	5.00	0.87
			633527	354.10	354.90	0.80	0.85	0.10	1.00	5.00	8.50
			633528	354.90	355.10	0.20	0.03	0.01	1.00	5.00	3.00
			633529	355.10	356.50	1.40	0.04	0.12	1.00	5.00	0.33
			633530	356.50	356.50	0.00	1.43	4.32	27.00	270.00	0.33
			633531	356.50	357.80	1.30	0.13	0.58	1.00	20.00	0.22
- CHERTY MUDSTONE FACIES: Consists of a greyish black monotonous siliceous, carbonaceous mudstone. It is most typically found overlying the thin bedded calcareous mudstone facies.											
- THIN BEDDED CALCAREOUS MUDSTONE FACIES: Consists of laminated carbonaceous mudstone containing 20-40% calcite, 40-55% quartz and 10-20% muscovite. Sulphides occur in laminae. In the XY area it is usually the lowest facies in the section to contain laminated sulphides.											
- CALCAREOUS MUDSTONE FACIES: Consists of grey to greyish black monotonous, calcareous siliceous carbonaceous mudstone. There are no feathery calcite beds or pyrite-calcite blebs in the facies, making it easily distinguishable from the CCMS.											

Selwyn Project Diamond Drill Log

Hole Number:
XYC-202

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		- GRADED LIMESTONE FACIES: Is a laminated argillaceous limestone with intercalated carbonaceous limestone laminae. The main rock type in the facies is laminated limestone with laminae up to 0.1-7mm thick. - LIGHT GREY BASAL LIMESTONE FACIES - LGLS: Consists of laminated argillaceous limestone. In the Anniv area it marks the end of the ACTM. It's not always present in the stratigraphy. - BASAL FACIES: This is a highly contorted and locally foliated carbonaceous mudstone. Unlike the other facies it is not repeated higher in the member. It appears locally to contain the slip zone of a major slump. The facies has only been observed in the YX area. It is 0.1-2m thick. The facies consists of massive carbonaceous siliceous mudstone with lenses and laminae of contorted, slightly carbonaceous chert. « 335.30- 337.10 Siliceous mudstone with thin laminae » « 337.10- 338.00 Light grey siliceous mudstone with faint laminae; microfaults are fairly developed. » « 338.00- 338.20 Black siliceous mudstone with thin py bands » « 338.20- 341.90 Siliceous mudstone with thin laminae » « 341.90- 346.90 Black siliceous mudstone with limestone nodules » « 346.90- 347.80 Grey limestone » « 347.80- 349.20 Black siliceous mudstone » « 349.20- 349.60 Limestone » « 349.60- 350.50 Siliceous mudstone with thin laminae »									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-202

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		« 350.50- 351.30 Black siliceous mudstone with limestone bands »									
		« 351.30- 352.50 Limestone breccia with qtz+_cal matrix »									
		« 352.50- 353.30 Black siliceous mudstone »									
		« 353.30- 354.90 Limestone breccia »									
		« 354.90- 357.80 Black siliceous mudstone interbanded with limestone; qtz veins are well developed »									
357.80	394.10	CCMS	633532	357.80	358.40	0.60	0.16	1.20	2.00	40.00	0.13
		CCMS – Calcareous Mudstone	633533	358.40	359.70	1.30	0.06	0.25	1.00	10.00	0.24
			633534	359.70	360.60	0.90	0.01	0.01	1.00	10.00	1.00
		Massive, calcareous, carbonaceous, dark grey mudstone. Most of the member is massive, but rare poorly defined bedding and pyrite-calcite micro-concretions are present. Most diagnostic structures are feathery calcite beds (=thin calcite-cemented concretions, many of them contain pyrite cores) and calcite pseudo-beds (= fibrous calcite vein parallel to bedding). « lm ca 5.00-10.00mm », « nodules py -3.00% 2.00-20.00mm »									
		Black carboneceous siliceous mudstone with faint py+_cal beds; laminated qtz+_cal thin veinlets are parallel to the beds; calcareous mudstone sections are found locally in gradational contact.									
		< @ 361.60 S0 defined by faint py beds S0 tca 40° >									
		< @ 369.40 S0 defined by faint py beds S0 tca 63° >									
		< @ 384.60 S0 defined by faint py beds S0 tca 55° >									
394.10	394.10	EOH									

Diamond Drill Log

Comprehensive Report for Hole:

XYC-201

Hole No.: XYC-201	Depth: 185.00 m	Horizontal Length: 0.00 m	Project: 1710
Location Data:			
Property:	Selwyn Project	Claim Name:	X 16
Mining District:	Selwyn Basin	Grant Number:	Y 64541
Province/Territory:	Yukon		
UTM Co-Ordinates & Altitude of Drill Hole Collar:			
UTM Easting:	489228.25 m	True Azimuth:	210.0 °
UTM Northing:	6926256.32 m	Hole Angle:	-66.0 °
Elevation (m):	1625.42 m	NTS Name:	Placer Creek
		NTS Number:	105I06
Grid Co-Ordinates of Drill Hole Collar:			
Grid Easting (m):	0.00 m	Grid Name:	HP 06
Grid Northing (m):	0.00 m	Grid Type:	100m
Grid Azimuth:	270.0 °		
Dimond Drilling Contract:			
Drilled By:	NL-03	Date Drilling Start:	08/18/2010
		Date Finish:	08/21/2010
Diamond Drill Core:			
Logged By:	Matthew Jodrey	Date Logging Start:	08/20/2010
		Date Finish:	08/23/2010
Legend for Core Logging Codes: PAX			
Core Size:	NQ	Cemented:	Yes
Casing Depth:	3.20 m	Casing Pulled:	Yes
Water Depth:	0.00 m	Overburden Depth:	3.20 m
Level:			
Section:		Drift:	

Selwyn Project

Diamond Drill Log

Survey Data for Hole

XYC-201

Hole Comments:

Lovely Daily Comments from David Legault:

Wed, Aug 18 --- drill move to set-up in morning

=====

Thu, Aug 19 ---

=====

Fri, Aug 20 --- Lots of fault gouge, broken core tight hole. USMS?

<i>Depth</i>	<i>Dip</i>	<i>Azimuth</i>
0.00	-66.0	210.0
48.20	-65.5	208.9
93.90	-64.9	202.1
139.60	-64.5	204.0
185.00	-63.5	206.3

Selwyn Project

Diamond Drill Log

Hole Number:
XYC-201

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
0.00	3.20	OVBR									
3.20	43.60	BSSM									
BSSM – Backside Siliceous Mudstone											
Devonian Siliceous Mudstone – Upper Chert Formation											
Greyish black laminated chert and siliceous mudstone. Randomly-oriented to bedding-parallel bioturbation is common in the bottom of the unit. « lm chrt 75.00-95.00% », « btrb 0.10-2.00cm », Includes squiggly medium grey bands and is locally inter-layered with calcareous ranges; faint beds are visible and defined by very fine grained pyrite + calcite. « 3.20- 17.70 light grey siliceous bioturbated mudstone; gradational contact with adjacent dark grey mudstone » ‹ @ 21.80 calcite +/- pyrite in faint beds So tca 61° › ‹ @ 38.70 faint pyrite beds SO tca 57° ›											
43.60	47.30	FLT									
Major carbonaceous fault likely responsible for the absense of Flaggy Mudstone in this drillhole. « fault »« gouge 20%»« rubble 20%»« broken 60%»											
47.30	133.50	USMS	631951	130.20	131.00	0.80	0.01	0.73	2.00	20.00	0.01
USMS – Upper Siliceous Mudstone			631952	131.00	131.70	0.70	0.01	0.20	1.00	5.00	0.05
Consists of interlaminated dark grey to black mudstone and light to medium grey chert. Regionally, a 1m thick graptolite zone occurs 15m below the top of the upper unit, this is usable as a horizon. The USMS is divided into 3 units. The Lower Unit contains abundant limestone concretions and Galena and sphalerite micro-concretions occur locally near the base of this unit. « gra , lm chrt			631953	131.70	132.50	0.80	0.02	0.14	1.00	5.00	0.14
			631954	132.50	133.50	1.00	0.49	1.03	1.00	30.00	0.48

Selwyn Project Diamond Drill Log

Hole Number:
XYC-201

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		-20.00% », « cg xtl sph crns ca 5.00-20.00cm », « bed chrt 10.00-15.00% », Includes abundant carbonate concretions and squiggly medium grey chert bands and light grey carbonate bands 3-8 mm thickness. « 53.60- 62.10 Broken range; includes minor gouge » ◁ @ 55.50 s0 tca 60° ▷ « 57.30- 58.00 carbonaceous fault »« rubble 30%»« gouge 5%» « 59.80- 60.70 fault »« rubble 30%»« gouge 5%» ◁ @ 68.20 planar parallel chert bands s0 tca 52° ▷ ◁ @ 82.40 planar parallel chert/carbonate bands s0 tca 58° ▷ « 85.30- 88.80 carbonaceous fault »« rubble 30%»« gouge 30%» ◁ @ 85.80 planar parallel chert/carbonate bands s0 tca 51° ▷ « 91.70- 108.80 major carbonaceous fault »« rubble 40%»« gouge 40%» « 108.80- 113.80 heavily broken zone » « 113.80- 118.20 fault »« rubble 40%»« gouge 20%» « 118.20- 130.90 heavily broken zone » ◁ @ 126.70 quartz-rich lamination in siliceous mudstone s0 tca 56° ▷ « 132.50- 133.50 fault »« rubble 70%»«gouge 20%»									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-201

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
133.50	157.10	ACTM	631955	133.50	133.90	0.40	1.42	10.02	3.00	280.00	0.14
ACTM – Active Member			631956	133.90	135.10	1.20	0.62	1.51	1.00	50.00	0.41
The ACTM consists of a repetitive, possibly rhythmic, sequence of intercalated carbonaceous mudstone, cherty mudstone, chert and limestone and locally contains economically significant Zn and Pb sulphides (see bold marked facies), mainly in its sections with well developed lamination. Because of its heterogeneity, the member is distinctive and easily identified. ===== The ACTM has 8 different facies: ===== - GREY CHERT FACIES: Consists of laminated medium light grey to medium dark grey chert. Mineralization: 95-99% quartz and up to 5% secondary calcite. - WHITISH GREY ZN-PB MUDSTONE FACIES: Is a laminated cherty rock containing up to 70% sulphides. Mineralization: quartz, sphalerite and galena are the major minerals with only minor amounts of pyrite and locally calcite. Sedimentary diagenetic structures are common and well displayed in the facies, such as: lamination, pseudo-beds, calcite nodules & limestone nodules and abundant water escape structures. Most obvious structure in facies is cross-cutting veins containing massive sphalerite and galena with minor pyrite. They range in width from 0.5 to 10mm. - THIN BEDDED CHERTY MUDSTONE FACIES: Consists of rhythmic intercalated laminae of chert, carbonaceous mudstone and minor micrite. This facies contains significant amounts of Zn and Pb sulphides. - CHERTY MUDSTONE FACIES: Consists of a greyish black monotonous siliceous, carbonaceous mudstone. It is most typically found overlying the thin bedded calcareous mudstone facies. - THIN BEDDED CALCAREOUS MUDSTONE FACIES: Consists of laminated			631957	135.10	136.30	1.20	0.33	1.39	1.00	40.00	0.24
			631958	136.30	136.90	0.60	0.13	0.84	1.00	20.00	0.15
			631959	136.90	137.70	0.80	0.32	1.17	1.00	40.00	0.27
			631960	137.70	138.80	1.10	0.55	1.74	1.00	50.00	0.32
			631961	137.70	138.80	1.10	0.34	2.19	1.00	60.00	0.16
			631962	138.80	139.30	0.50	1.99	3.95	1.00	110.00	0.50
			631963	139.30	139.80	0.50	0.61	2.15	1.00	60.00	0.28
			631964	139.80	140.10	0.30	1.26	8.18	3.00	230.00	0.15
			631965	140.10	140.90	0.80	1.61	4.22	1.00	110.00	0.38
			631966	140.90	141.20	0.30	1.25	6.41	1.00	180.00	0.20
			631967	141.20	142.00	0.80	0.38	0.77	1.00	20.00	0.49
			631968	142.00	142.50	0.50	0.13	0.49	1.00	10.00	0.27
			631969	142.50	143.30	0.80	0.08	0.92	1.00	20.00	0.09
			631970	143.30	143.30	0.00	0.01	0.01	1.00	5.00	2.00
			631971	143.30	143.90	0.60	0.03	0.50	1.00	10.00	0.06
			631972	143.90	144.90	1.00	1.77	0.78	3.00	20.00	2.27
			631973	144.90	146.00	1.10	0.70	1.87	2.00	40.00	0.37
			631974	146.00	146.90	0.90	0.16	0.87	1.00	30.00	0.18
			631975	146.90	147.70	0.80	0.16	0.48	2.00	20.00	0.33
			631976	147.70	148.50	0.80	0.20	2.11	3.00	60.00	0.09
			631977	148.50	149.80	1.30	0.20	0.50	1.00	10.00	0.40
			631978	149.80	151.10	1.30	0.38	1.73	3.00	40.00	0.22
			631979	151.10	152.00	0.90	0.57	1.60	5.00	50.00	0.36
			631980	152.00	152.00	0.00	0.93	1.35	216.00	90.00	0.69
			631981	152.00	153.00	1.00	0.09	1.11	3.00	40.00	0.08
			631982	153.00	153.70	0.70	0.23	0.73	3.00	20.00	0.32
			631983	153.70	154.80	1.10	0.02	0.06	1.00	5.00	0.33
			631984	154.80	156.00	1.20	0.01	0.01	1.00	5.00	2.00
			631985	156.00	157.00	1.00	0.04	0.12	1.00	5.00	0.33

Selwyn Project Diamond Drill Log

Hole Number:
XYC-201

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		carbonaceous mudstone containing 20-40% calcite, 40-55% quartz and 10-20% muscovite. Sulphides occur in laminae. In the XY area it is usually the lowest facies in the section to contain laminated sulphides. - CALCAREOUS MUDSTONE FACIES: Consists of grey to greyish black monotonous, calcareous siliceous carbonaceous mudstone. There are no feathery calcite beds or pyrite-calcite blebs in the facies, making it easily distinguishable from the CCMS. - GRADED LIMESTONE FACIES: Is a laminated argillaceous limestone with intercalated carbonaceous limestone laminae. The main rock type in the facies is laminated limestone with laminae up to 0.1-7mm thick. - LIGHT GREY BASAL LIMESTONE FACIES - LGLS: Consists of laminated argillaceous limestone. In the Anniv area it marks the end of the ACTM. It's not always present in the stratigraphy. - BASAL FACIES: This is a highly contorted and locally foliated carbonaceous mudstone. Unlike the other facies it is not repeated higher in the member. It appears locally to contain the slip zone of a major slump. The facies has only been observed in the YX area. It is 0.1-2m thick. The facies consists of massive carbonaceous siliceous mudstone with lenses and laminae of contorted, slightly carbonaceous chert. « 133.50- 133.90 Laminated dark grey calcareous mudstone with strong visible mineralization; NITON: 12.6% Zn, 4.5% Pb » « 133.90- 136.30 Light grey limestone with no visible mineralization; NITON: 1.1% Zn, 0.9% Pb » « 136.30- 136.90 Unlaminated calcareous mudstone; totally broken-up; no visible mineralization; NITON: 1.2% Zn, 0.4% Pb »									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-201

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		« 136.90- 137.70 Weakly laminated light grey limestone; NITON: 1.1% Zn, 0.6% Pb »									
		« 137.70- 138.80 Mix of light grey unlaminated limestone and locally laminated calcareous mudstone; low visible mineralization; NITON: 1.4% Zn, 0.4% Pb »									
		« 138.80- 139.30 laminated calcareous mudstone with moderate visible mineralization; NITON: 3.4% Zn, 1.2% Pb »									
		« 139.30- 139.80 Light grey unlaminated limestone with minor laminated calcareous mudstone; weak visible mineralization; NITON: 1.2% Zn, 0.5% Pb »									
		« 139.80- 140.10 Laminated calcareous mudstone with moderate visible mineralization with minor light grey limestone; NITON: 6.5% Zn, 2.0 % Pb »									
		« 140.10- 140.90 Light grey limestone with laminated calcareous mudstone; shows visible mineralization including galena stringers; NITON: 1.4% Zn, 0.5% Pb »									
		« 140.90- 141.20 Dark grey laminated calcareous mudstone with weak visible mineralization; NITON: 3.0% Zn, 1.1% Pb »									
		« 141.20- 142.00 Fault zone »« Rubble 10%»« Gouge 10%»« Interbedded limestone and calcareous mudstone within the fault zone, with no visible mineralization; NITON: 0.3% Zn, 0.3% Pb »									
		« 142.00- 142.50 Weakly laminated weakly calcareous mudstone with no visible mineralization; NITON: 0.1% Zn, 0.1% Pb »									
		« 142.50- 146.90 Broken, mixed limestone and weakly laminated calcareous mudstone with no visible mineralization; NITON: 0.1% Zn, 0.1% Pb »									
		« 146.90- 148.50 Unlaminated calcareous mudstone; NITON: 0.9% Zn, 0.3% Pb »									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-201

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		« 148.50- 149.80 Light grey laminated limestone; NITON: 0.3% Zn, 0.1% Pb »									
		« 149.80- 151.10 Unlaminated calcareous mudstone; NITON: 0.9% Zn, 0.4% Pb »									
		« 151.10- 152.00 weakly laminated calcareous mudstone; NITON: 1.0 % Zn, 0.3% Pb »									
		« 152.00- 153.70 unlaminated calcareous mudstone; NITON: 0.7% Zn, 0.3% Pb »									
		« 153.70- 157.00 Light grey basal limestone facies with no visible mineralization; NITON: 0.1% Pb, Zn: nil »									
157.10	185.00	CCMS									
		CCMS – Calcareous Mudstone									
		Massive, calcareous, carbonaceous, dark grey mudstone. Most of the member is massive, but rare poorly defined bedding and pyrite-calcite micro-concretions are present. Most diagnostic structures are feathery calcite beds (=thin calcite-cemented concretions, many of them contain pyrite cores) and calcite pseudo-beds (= fibrous calcite vein parallel to bedding).									
		« lm ca 5.00-10.00mm », « nodules py -3.00% 2.00-20.00mm »,									
		« 157.10- 177.10 very broken-up range »									
		< @ 161.10 1.5 cm thick calcite-rich beds s0 tca 85° >									
		< @ 161.20 ameoid galena stringer with pyrite - 1cm thick >									
		« 165.30- 166.80 fault »« fault breccia 20%»« flt gouge 20%»									



Selwyn Project Diamond Drill Log

Hole Number:
XYC-201

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		« 169.00- 172.70 fault » < @ 174.30 s0 tca 70° > « 175.40- 176.90 carbonaceous fault »« flt breccia 70%»« flt gouge 25%» < @ 178.80 s0 tca 66° >									
185.00	185.00	EOH									

Selwyn Project

Diamond Drill Log

Comprehensive Report for Hole:

XYC-200

Hole No.: XYC-200	Depth: 255.40 m	Horizontal Length: 0.00 m	Project: 1710
Location Data:			
Property:	Selwyn Project	Claim Name:	X 13
Mining District:	Selwyn Basin	Grant Number:	Y 64538
Province/Territory:	Yukon		
UTM Co-Ordinates & Altitude of Drill Hole Collar:			
UTM Easting:	489067.22 m	True Azimuth:	223.0 °
UTM Northing:	6926360.98 m	Hole Angle:	-78.0 °
Elevation (m):	1647.00 m	NTS Name:	Placer Creek
		NTS Number:	105I06
Grid Co-Ordinates of Drill Hole Collar:			
Grid Easting (m):	0.00 m	Grid Name:	HP 06
Grid Northing (m):	0.00 m	Grid Type:	100m
Grid Azimuth:	283.0 °		
Dimond Drilling Contract:			
Drilled By:	NL-03	Date Drilling Start:	08/13/2010
		Date Finish:	08/17/2010
Diamond Drill Core:			
Logged By:	Gabe Xue	Date Logging Start:	08/18/2010
		Date Finish:	08/19/2010
Legend for Core Logging Codes: PAX			
Core Size:	NQ	Cemented:	Yes
Casing Depth:	5.80 m	Casing Pulled:	Yes
Water Depth:	0.00 m	Overburden Depth:	5.80 m
Level:	Section:	Drift:	

Selwyn Project

Diamond Drill Log

Survey Data for Hole

XYC-200

Hole Comments:

Sat, Aug 14 --- The new CS1000 arrived around 7pm at setup #6. I got there around 7.15 to line it up. It took a while before they got the drill level. They put in 15' casing and the total depth at morning shift change was 10.4m. It looks like weathered FLMD, possibly weathered bioturbated BSSM. Not enough core to make the call.

=====

Sun, Aug 15 --- At morning shift change the total depth was 78.8m, in BSSM.

=====

Mon, Aug 16 --- The total depth was 124m at morning shift change; right now in USMS. The FLMD-USMS contact was approximately at 109m.

=====

Tue, Aug 17 --- Went through a small fault or fracture, still in USMS

<i>Depth</i>	<i>Dip</i>	<i>Azimuth</i>
0.00	-78.0	223.0
51.20	-77.8	222.4
91.40	-76.9	221.2
139.60	-75.8	218.6
182.30	-75.3	221.6
240.20	-75.0	219.6
254.80	-74.6	220.4

Selwyn Project

Diamond Drill Log

Hole Number:
XYC-200

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
0.00	5.00	OVBR									
5.00	84.10	BSSM									
<i>BSSM – Backside Siliceous Mudstone</i>											
<i>Devonian Siliceous Mudstone – Upper Chert Formation</i>											
<i>Greyish black laminated chert and siliceous mudstone. Randomly-oriented to bedding-parallel bioturbation is common in the bottom of the unit. « lm chrt 75.00-95.00% », « btrb 0.10-2.00cm »</i>											
<i>Few cherty bands are seen and beds are weakly defined by very fine grained py; black streches of bioturbation are visible only in medium grey sections and graded limestone nodules are apparent locally.</i>											
<i>◁ @ 15.30 S0 defined by faint py beds S0 tca 50° ▷</i>											
<i>« 20.70- 31.40 Fault zone with 70% of broken BSSM »« flt gg 10%»« flt bx 20%»</i>											
<i>« 47.50- 61.90 Grey bioturbated mudstone with several black siliceous mudstone »</i>											
<i>◁ @ 56.30 S0 defined by faint py beds S0 tca 31° ▷</i>											
<i>« 61.90- 71.30 Light grey siliceous clasts supported breccia with qtz+_calcite matrix »</i>											
84.10	107.30	FLMD									
<i>FLMD – Flaggy Mudstone Formation</i>											
<i>Dark grey mudstone in the upper portions of the unit grading into light grey mudstone to siltstone. Contains abundant wispy bioturbation which ranges from randomly-oriented at the top of the unit to bedding-parallel throughout the majority of the unit. Darker upper section has a strong fetid odour along</i>											

Selwyn Project Diamond Drill Log

Hole Number:
XYC-200

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
broken surfaces. « btrb 0.10-2.00cm », « cg xtl crns ca 1.00-5.00% 5.00-150.00cm », « crns py 1.00-5.00% 0.10-0.50mm » « 84.10- 87.50 Fault zone with 80% of broken FLMD and BSSM core »« flt gg 5%»« flt bx 15%» « @ 104.10 S0 defined by bioturbations S0 tca 36° » « 106.10- 107.30 Well developed qtz veining »											
107.30	180.10	USMS	631901	133.40	133.70	0.30	0.08	0.01	1.00	5.00	16.00
USMS – Upper Siliceous Mudstone			631902	133.70	133.85	0.15	0.69	1.27	3.00	30.00	0.54
Consists of interlaminated dark grey to black mudstone and light to medium grey chert. Regionally, a 1m thick graptolite zone occurs 15m below the top of the upper unit, this is usable as a horizon. The USMS is divided into 3 units. The Lower Unit contains abundant limestone concretions and Galena and sphalerite micro-concretions occur locally near the base of this unit. « gra , lm chrt -20.00% », « cg xtl sph crns ca 5.00-20.00cm », « bed chrt 10.00-15.00% » Medium grey distorted cherty bands are in various thickness and calcareous mudstone sections are found locally. « 115.60- 117.00 Fault zone with 70% of USMS broken core »« flt gg 10%»« flt bx 20%» « 133.70- 133.75 ACTM-like light grey siliceous mudstone with thin laminae » « 150.00- 150.90 Fault zone with 60% of broken core »« flt gg 20%»« flt bx 20%» « 162.50- 164.50 Qtz +_Cal vein containing 5% black clasts »			631903	133.85	134.05	0.20	0.01	0.12	1.00	5.00	0.08
			631904	179.60	180.10	0.50	0.01	0.20	3.00	5.00	0.05

Selwyn Project Diamond Drill Log

Hole Number:
XYC-200

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
« 170.10- 173.70 Fault zone with 70% of broken core »« flt gg 10%»« flt bx 20%»											
180.10	200.30	ACTM	631905	180.10	181.10	1.00	0.91	3.69	3.00	150.00	0.25
ACTM – Active Member			631906	181.10	182.10	1.00	0.33	2.69	1.00	80.00	0.12
			631907	182.10	183.10	1.00	0.51	2.91	2.00	80.00	0.18
<i>The ACTM consists of a repetitive, possibly rhythmic, sequence of intercalated carbonaceous mudstone, cherty mudstone, chert and limestone and locally contains economically significant Zn and Pb sulphides (see bold marked facies), mainly in its sections with well developed lamination. Because of its heterogeneity, the member is distinctive and easily identified.</i>			631908	183.10	183.60	0.50	0.28	0.81	1.00	20.00	0.35
			631909	183.60	184.10	0.50	0.54	1.92	1.00	50.00	0.28
			631910	184.10	184.40	0.30	0.73	2.90	1.00	80.00	0.25
			631911	184.10	184.40	0.30	0.37	2.36	1.00	60.00	0.16
			631912	184.40	185.90	1.50	0.79	3.65	1.00	100.00	0.22
=====			631913	185.90	187.40	1.50	1.34	0.89	4.00	30.00	1.51
<i>The ACTM has 8 different facies:</i>			631914	187.40	188.20	0.80	0.54	2.02	3.00	60.00	0.27
=====			631915	188.20	189.20	1.00	0.11	0.22	1.00	5.00	0.50
			631916	189.20	190.20	1.00	0.03	0.06	1.00	5.00	0.50
			631917	190.20	191.20	1.00	0.20	0.19	1.00	5.00	1.05
<i>- GREY CHERT FACIES: Consists of laminated medium light grey to medium dark grey chert. Mineralization: 95-99% quartz and up to 5% secondary calcite.</i>			631918	191.20	192.20	1.00	0.15	0.81	3.00	20.00	0.19
			631919	192.20	193.30	1.10	0.43	1.95	5.00	50.00	0.22
			631920	193.30	193.30	0.00	0.01	0.01	1.00	5.00	2.00
<i>- WHITISH GREY ZN-PB MUDSTONE FACIES: Is a laminated cherty rock containing up to 70% sulphides. Mineralization: quartz, sphalerite and galena are the major minerals with only minor amounts of pyrite and locally calcite. Sedimentary diagenetic structures are common and well displayed in the facies, such as: lamination, pseudo-beds, calcite nodules & limestone nodules and abundant water escape structures. Most obvious structure in facies is cross-cutting veins containing massive sphalerite and galena with minor pyrite. They range in width from 0.5 to 10mm.</i>			631921	193.30	194.80	1.50	0.50	0.89	4.00	30.00	0.56
			631922	194.80	195.70	0.90	0.07	0.71	3.00	20.00	0.10
			631923	195.70	196.40	0.70	0.10	0.92	3.00	30.00	0.11
			631924	196.40	197.30	0.90	0.31	0.59	4.00	20.00	0.53
			631925	197.30	198.00	0.70	0.73	0.92	5.00	30.00	0.79
			631926	198.00	199.00	1.00	0.04	0.04	1.00	5.00	1.00
			631927	199.00	200.30	1.30	0.01	0.03	1.00	5.00	0.33
<i>- THIN BEDDED CHERTY MUDSTONE FACIES: Consists of rhythmic intercalated laminae of chert, carbonaceous mudstone and minor micrite. This facies contains significant amounts of Zn and Pb sulphides.</i>											
<i>- CHERTY MUDSTONE FACIES: Consists of a greyish black monotonous siliceous,</i>											

Selwyn Project Diamond Drill Log

Hole Number:
XYC-200

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		carbonaceous mudstone. It is most typically found overlying the thin bedded calcareous mudstone facies. - THIN BEDDED CALCAREOUS MUDSTONE FACIES: Consists of laminated carbonaceous mudstone containing 20-40% calcite, 40-55% quartz and 10-20% muscovite. Sulphides occur in laminae. In the XY area it is usually the lowest facies in the section to contain laminated sulphides. - CALCAREOUS MUDSTONE FACIES: Consists of grey to greyish black monotonous, calcareous siliceous carbonaceous mudstone. There are no feathery calcite beds or pyrite-calcite blebs in the facies, making it easily distinguishable from the CCMS. - GRADED LIMESTONE FACIES: Is a laminated argillaceous limestone with intercalated carbonaceous limestone laminae. The main rock type in the facies is laminated limestone with laminae up to 0.1-7mm thick. - LIGHT GREY BASAL LIMESTONE FACIES - LGLS: Consists of laminated argillaceous limestone. In the Anniv area it marks the end of the ACTM. It's not always present in the stratigraphy. - BASAL FACIES: This is a highly contorted and locally foliated carbonaceous mudstone. Unlike the other facies it is not repeated higher in the member. It appears locally to contain the slip zone of a major slump. The facies has only been observed in the YX area. It is 0.1-2m thick. The facies consists of massive carbonaceous siliceous mudstone with lenses and laminae of contorted, slightly carbonaceous chert. « 180.10- 188.20 Fault zone with 30% of broken core, pieces of dark grey thin laminated siliceous mudstone are seen »« flt gg 30%»« flt bx 40%» « 188.20- 190.20 Medium grey graded limestone with black convolute stretches »									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-200

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		« 190.20- 191.10 Grey very calcareous mudstone with thin laminae »									
		« 191.10- 192.20 Medium grey graded limestone »									
		« 192.20- 196.40 Black siliceous mudstone with faint defined yellowish grey laminae »									
		« 196.40- 198.00 Black siliceous mudstone containing lots of medium grey wormy calcareous bands in thickness of 3-10mm »									
		« 198.00- 200.30 Light grey limestone with black laminae »									
200.30	255.40	CCMS	631928	200.30	200.90	0.60	0.01	0.01	1.00	5.00	2.00
		CCMS – Calcareous Mudstone	631929	200.90	200.90	0.00	0.97	1.31	226.00	90.00	0.74
		Massive, calcareous, carbonaceous, dark grey mudstone. Most of the member is massive, but rare poorly defined bedding and pyrite-calcite micro-concretions are present. Most diagnostic structures are feathery calcite beds (=thin calcite-cemented concretions, many of them contain pyrite cores) and calcite pseudo-beds (= fibrous calcite vein parallel to bedding). « lm ca 5.00-10.00mm », « nodules py -3.00% 2.00-20.00mm »									
		Black siliceous mudstone interlayered with dark grey calcareous mudstone, and faint beds defined by very fine grained py+_cal are visible locally.									
		« 200.30- 205.90 Fault zone with 50% of broken CCMS core »« flt gg 20%»« flt bx 30%»									
		< @ 208.00 S0 defined by faint py+_cal beds S0 tca 62° >									
		< @ 224.40 S0 defined by faint py+_cal beds S0 tca 55° >									
		< @ 236.80 S0 defined by faint py+_cal beds S0 tca 50° >									



Selwyn Project Diamond Drill Log

Hole Number:
XYC-200

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		< @ 250.80 S0 defined by faint py+ _ cal beds S0 tca 70° >									
255.40	255.40	EOH									

Diamond Drill Log

Comprehensive Report for Hole:

XYC-199

Hole No.: XYC-199	Depth: 189.00 m	Horizontal Length: 0.00 m	Project: 1710
Location Data:			
Property:	Selwyn Project	Claim Name:	X 16
Mining District:	Selwyn Basin	Grant Number:	Y 64541
Province/Territory:	Yukon		
UTM Co-Ordinates & Altitude of Drill Hole Collar:			
UTM Easting:	489172.39 m	True Azimuth:	208.0 °
UTM Northing:	6926169.13 m	Hole Angle:	-75.0 °
Elevation (m):	1611.35 m	NTS Name:	Placer Creek
		NTS Number:	105I06
Grid Co-Ordinates of Drill Hole Collar:			
Grid Easting (m):	0.00 m	Grid Name:	HP 06
Grid Northing (m):	0.00 m	Grid Type:	100m
Grid Azimuth:	268.0 °		
Dimond Drilling Contract:			
Drilled By:	NL-01	Date Drilling Start:	08/10/2010
		Date Finish:	08/13/2010
Diamond Drill Core:			
Logged By:	Jelle De Bruyckere	Date Logging Start:	08/15/2010
		Date Finish:	08/15/2010
Legend for Core Logging Codes: PAX			
Core Size:	NQ	Cemented:	Yes
Casing Depth:	6.20 m	Casing Pulled:	Yes
Water Depth:	0.00 m	Overburden Depth:	6.20 m
Level:	Section:	Drift:	

Selwyn Project

Diamond Drill Log

Survey Data for Hole

XYC-199

Hole Comments:

Wed, Aug 11 --- XYC-197 got shut down and cemented yesterday morning. The mobilization commenced in the morning and was finished in the afternoon. 7.6m of casing was put in. Recovery started at 6.1m. Total depth at morning shift change is 28m. The hole collared in FLMD, but right now we're in a fault which started at a depth of 17.4m.

=====

Thu, Aug 12 ---Total depth at morning shift change was 83m. They emerged out of the fault and are now in USMS.

=====

Fri, Aug 13 --- Yesterday's dayshift drilled through ACTM, from 82.75m to 104.2m. Not the greatest ACTM, but there is at least one 90cm long section of very high grade core (>30% combined) and another section of 50cm (>18% combined). We're well in footwall rock (CCMS) now at a total depth of 174.7m. I've shut down the drill. The 56 will be put on hold for some general repair and maintenance and will be replaced by the second CS1000 in the meanwhile.

=====

Sat, Aug 14 --- XYC-199 got shut down yesterday, but they drilled a bit more during morning though, because it would take until late afternoon before the new drill would arrive at XY Central. The old 56 drill will get pulled back to camp today for general maintenance and repair.

<i>Depth</i>	<i>Dip</i>	<i>Azimuth</i>
0.00	-75.0	208.0
62.50	-74.7	207.9
102.10	-74.2	207.4
147.80	-73.6	207.5
189.00	-73.1	208.6

Selwyn Project Diamond Drill Log

Hole Number:
XYC-199

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
0.00	6.20	OVBR									
6.20	18.90	FLMD									
<i>FLMD – Flaggy Mudstone Formation</i>											
<i>Dark grey mudstone in the upper portions of the unit grading into light grey mudstone to siltstone. Contains abundant wispy bioturbation which ranges from randomly-oriented at the top of the unit to bedding-parallel throughout the majority of the unit. Darker upper section has a strong fetid odour along broken surfaces. « btrb 0.10-2.00cm », « cg xtl crns ca 1.00-5.00% 5.00-150.00cm », « crns py 1.00-5.00% 0.10-0.50mm »</i>											
<i>< @ 8.30 S0 defined by bioturbations S0 tca 31° ></i>											
<i>< @ 11.30 S0 defined by bioturbations S0 tca 33° ></i>											
<i>« 12.70- 18.90 Flt »« Flt gg 25%»« Flt bx 40%»« brco 30%»</i>											
<i>Note that the fault actually ranges from 12.7m to 26.3m. From 12.7m to 18.9m FLMD is recognizable. From 18.9m to 26.3m USMS is recognizable.</i>											
18.90	79.70	USMS	628451	79.20	79.70	0.50	0.05	0.04	1.00	5.00	1.25
<i>USMS – Upper Siliceous Mudstone</i>											
<i>Consists of interlaminated dark grey to black mudstone and light to medium grey chert. Regionally, a 1m thick graptolite zone occurs 15m below the top of the upper unit, this is usable as a horizon. The USMS is divided into 3 units. The Lower Unit contains abundant limestone concretions and Galena and sphalerite micro-concretions occur locally near the base of this unit. « gra , lm chrt -20.00% », « cg xtl sph crns ca 5.00-20.00cm », « bed chrt 10.00-15.00% »</i>											
<i>« 18.90- 26.30 Flt »« Flt gg 25%»« flt bx 40%»« brco 30%»</i>											
<i>« 18.90- 79.70 The majority of the chert bands and squiggly quartz+calcite+pyrite bands are contorted in this section; making it difficult to measure the S0 tca »</i>											

Selwyn Project Diamond Drill Log

Hole Number:
XYC-199

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
< @ 59.80	S0 defined by parallel uncontorted chert bands S0 tca 56°	>									
< @ 63.80	S0 defined by parallel uncontorted chert bands S0 tca 55°	>									
< @ 65.10	S0 defined by parallel uncontorted chert bands S0 tca 61°	>									
79.70	104.30	ACTM	628452	79.70	80.70	1.00	1.64	1.49	4.00	40.00	1.10
ACTM – Active Member			628453	80.70	81.70	1.00	1.36	0.30	3.00	5.00	4.53
			628454	81.70	82.70	1.00	0.01	0.25	1.00	5.00	0.04
			628455	82.70	83.10	0.40	0.88	11.22	2.00	330.00	0.08
			628456	83.10	84.10	1.00	4.45	12.79	4.00	530.00	0.35
			628457	84.10	84.90	0.80	1.07	4.92	1.00	120.00	0.22
			628458	84.90	85.80	0.90	2.63	6.30	2.00	140.00	0.42
			628459	85.80	86.10	0.30	0.18	1.80	1.00	50.00	0.10
			628460	86.10	87.20	1.10	0.17	1.33	1.00	40.00	0.13
			628461	86.10	87.20	1.10	0.17	1.11	1.00	30.00	0.15
			628462	87.20	87.90	0.70	0.13	1.16	1.00	30.00	0.11
			628463	87.90	88.80	0.90	0.05	0.84	1.00	20.00	0.06
			628464	88.80	88.90	0.10	6.20	9.81	2.00	270.00	0.63
			628465	88.90	89.70	0.80	0.28	1.57	1.00	50.00	0.18
			628466	89.70	90.60	0.90	2.29	6.27	1.00	180.00	0.37
			628467	90.60	91.20	0.60	12.57	20.76	3.00	1090.00	0.61
			628468	91.20	91.60	0.40	11.34	18.38	3.00	980.00	0.62
			628469	91.60	92.30	0.70	0.34	0.17	1.00	5.00	2.00
			628470	92.30	92.30	0.00	0.03	0.03	1.00	5.00	1.00
			628471	92.30	93.30	1.00	0.12	0.16	1.00	5.00	0.75
			628472	93.30	94.50	1.20	0.15	0.52	1.00	10.00	0.29
			628473	94.50	95.00	0.50	0.12	0.97	1.00	20.00	0.12
			628474	95.00	96.00	1.00	0.46	1.49	1.00	30.00	0.31
			628475	96.00	97.00	1.00	0.09	0.14	1.00	5.00	0.64
			628476	97.00	98.00	1.00	0.21	0.94	1.00	30.00	0.22
			628477	98.00	99.10	1.10	0.29	1.57	3.00	40.00	0.18
			628478	99.10	100.10	1.00	0.13	0.58	1.00	10.00	0.22
			628479	100.10	101.00	0.90	0.33	2.53	2.00	60.00	0.13
			628480	101.00	101.00	0.00	6.36	6.77	71.00	180.00	0.94
			628481	101.00	102.10	1.10	0.06	1.26	1.00	40.00	0.05

Selwyn Project Diamond Drill Log

Hole Number:
XYC-199

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
carbonaceous mudstone. It is most typically found overlying the thin bedded calcareous mudstone facies. - THIN BEDDED CALCAREOUS MUDSTONE FACIES: Consists of laminated carbonaceous mudstone containing 20-40% calcite, 40-55% quartz and 10-20% muscovite. Sulphides occur in laminae. In the XY area it is usually the lowest facies in the section to contain laminated sulphides. - CALCAREOUS MUDSTONE FACIES: Consists of grey to greyish black monotonous, calcareous siliceous carbonaceous mudstone. There are no feathery calcite beds or pyrite-calcite blebs in the facies, making it easily distinguishable from the CCMS. - GRADED LIMESTONE FACIES: Is a laminated argillaceous limestone with intercalated carbonaceous limestone laminae. The main rock type in the facies is laminated limestone with laminae up to 0.1-7mm thick. - LIGHT GREY BASAL LIMESTONE FACIES - LGLS: Consists of laminated argillaceous limestone. In the Anniv area it marks the end of the ACTM. It's not always present in the stratigraphy. - BASAL FACIES: This is a highly contorted and locally foliated carbonaceous mudstone. Unlike the other facies it is not repeated higher in the member. It appears locally to contain the slip zone of a major slump. The facies has only been observed in the YX area. It is 0.1-2m thick. The facies consists of massive carbonaceous siliceous mudstone with lenses and laminae of contorted, slightly carbonaceous chert. « 79.70- 82.70 Cherty mudstone. No lamination. One visible galena bleb. Mineralization: 0.7% Zn & 0.7% Pb » « 82.70- 83.10 Siliceous mudstone with fairly well developed lamination. Visible sphalerite. Mineralization: 8.7% Zn & 2.4% Pb »			628482	102.10	103.10	1.00	0.18	0.98	2.00	30.00	0.18
			628483	103.10	104.30	1.20	0.03	0.01	1.00	5.00	6.00

Selwyn Project Diamond Drill Log

Hole Number:
XYC-199

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		« 83.10- 84.10 Siliceous mudstone with well developed lamination, crosscutting sphalerite stringers, galena blebs and galena stringers. Mineralization: 12.0% Zn & 8.0% Pb »									
		« 84.10- 85.80 Siliceous mudstone with well developed lamination, calcite veins, limestone clasts , galena blebs and galena stringers. Mineralization: 1.5% Zn & 3.5% Pb »									
		« 85.80- 86.10 Limestone »									
		« 86.10- 87.20 Very calcareous mudstone and limestone clasts. Faint mineralization: 0.4% Zn & 0.0% Pb »									
		« 87.20- 88.80 Very dark grey carbonaceous siliceous mudstone. Mineralization 0.7% Zn & 0.3% Pb »									
		« 88.80- 88.90 High Grade. Siliceous mudstone with well developed lamination. Lots of visible sphalerite and galena. Mineralization: 18.0% Zn & 12.0% Pb »									
		« 88.90- 89.70 Very calcareous mudstone and limestone. Mineralization: 1.2% Zn & 0.7% Pb »									
		« 89.70- 90.60 Broken up calcareous mudstone. Mineralization: 3.3% Zn & 1.7% Pb »									
		« 90.60- 91.60 High Grade. Massive sulphides (Sphalerite and Galena). Tons of visible sphalerite (thick bands and crystals). Minor calcite. Mineralization: 22.0% Zn & 13.0% Pb »									
		« 91.60- 94.50 Calcareous mudstone with intercalated limestone. Faint mineralization: 0.3% Zn & 0.0% Pb. Pyrite is present. »									
		« 94.50- 95.00 Barren siliceous mudstone with calcite veining. »									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-199

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		« 95.00- 101.00 Calcareous mudstone with intercalated limestone. Thinly bedded, locally contorted. » « 101.00- 103.10 Flt »« flt gg 20%»« flt bx 60%»« brco 20%»« Faint mineralization: 0.8% Zn & 0.0% Pb » « 103.10- 104.30 Light Grey Basal Limestone »									
104.30	189.00	CCMS	628484	104.30	104.80	0.50	0.04	0.07	1.00	5.00	0.57
		CCMS – Calcareous Mudstone Massive, calcareous, carbonaceous, dark grey mudstone. Most of the member is massive, but rare poorly defined bedding and pyrite-calcite micro-concretions are present. Most diagnostic structures are feathery calcite beds (=thin calcite-cemented concretions, many of them contain pyrite cores) and calcite pseudo-beds (= fibrous calcite vein parallel to bedding). « lm ca 5.00-10.00mm », « nodules py -3.00% 2.00-20.00mm » « 104.50- 121.50 Flt »« flt gg 5%»« flt bx 20%»« brco 60%»« Section is fairly badly broken up. » < @ 141.50 S0 defined by faint pyrite beds S0 tca 54° > < @ 144.30 S0 defined by faint pyrite beds S0 tca 68° > < @ 147.70 S0 defined by faint pyrite beds S0 tca 65° > < @ 149.50 S0 defined by very faint pyrite beds S0 tca 63° > < @ 166.40 S0 defined by faint pyrite beds S0 tca 59° > < @ 184.50 S0 defined by faint pyrite beds in very calcareous mudstone S0 tca 59° > < @ 187.40 S0 defined by faint pyrite beds in very calcareous mudstone S0 tca 70° >									
189.00	189.00	EOH									

Selwyn Project

Diamond Drill Log

Comprehensive Report for Hole:

XYC-198

Hole No.: XYC-198	Depth: 561.60 m	Horizontal Length: 0.00 m	Project: 1710
Location Data:			
Property:	Selwyn Project	Claim Name:	X 4
Mining District:	Selwyn Basin	Grant Number:	Y 64529
Province/Territory:	Yukon		
UTM Co-Ordinates & Altitude of Drill Hole Collar:			
UTM Easting:	488725.19 m	True Azimuth:	230.0 °
UTM Northing:	6926773.29 m	Hole Angle:	-90.0 °
Elevation (m):	1727.65 m	NTS Name:	Placer Creek
		NTS Number:	105I06
Grid Co-Ordinates of Drill Hole Collar:			
Grid Easting (m):	0.00 m	Grid Name:	HP 06
Grid Northing (m):	0.00 m	Grid Type:	100m
Grid Azimuth:	290.0 °		
Dimond Drilling Contract:			
Drilled By:	NL-02	Date Drilling Start:	08/09/2010
		Date Finish:	08/24/2010
Diamond Drill Core:			
Logged By:	Matt and Jelle	Date Logging Start:	08/13/2010
		Date Finish:	08/27/2010
Legend for Core Logging Codes: PAX			
Core Size:	NQ3	Cemented:	Yes
Casing Depth:	55.00 m	Casing Pulled:	Yes
Water Depth:	0.00 m	Overburden Depth:	55.00 m
Level:	Section:	Drift:	

Selwyn Project

Diamond Drill Log

Survey Data for Hole

XYC-198

Hole Comments:

Tue, Aug 10 ---XYC-196 got shut down at 579.7m, just before lunchtime. The drill got moved to #19 late afternoon and was lined up around in the early evening; note that the AZI is 230, and DIP is -87 as per JJ changes on Friday Aug 6th. Last night 69' of casing was put in place in XYC-198.

=====

Wed, Aug 11 --- Casing is still being put in. Right now there is 130' of casing in the hole; they added 61' of casing in the past 24hrs.

=====

Thu, Aug 12 ---Casing is 180' deep. The hole is right now in BSSM at a total depth of 84.6m. They encountered a fault from the very beginning and we might be out of it at 81.6m.

=====

Fri, Aug 13 --- The hole is at 150.6m, still in BSSM. Drilling is going well.

=====

Sat, Aug 14 --- The hole is at 186.6m and still in BSSM. Very competent core. The water pump ran out of fuel last night and there was some trouble to get it started again. It's all fixed now.

=====

Sun, Aug 15 ---The hole is at 246.6m and still in BSSM. Very competent core.

=====

Mon, Aug 16 --- The hole is at 280.6m and still in BSSM.

=====

Tue, Aug 17 ---Still in BSSM, attempted a packer test last night, defective tool and we will have to try again for packer test

=====

Wed, Aug 18 --- Footage was wrongly reported yesterday, Still in BSSM, went through very bad ground, NS dropped the crown last night, tube and devicore tool is stuck in core barrel, putting in new core barrel, will drill the crown and we are retrieving the devicore and tube from the old core barrel. NS driller fired on his way back to Whitehorse

=====

Thu, Aug 19 ---Tried drilling through the crown, no success. Pulled rods to put a new bit, cemented 6 inch at the bottom to lock the crown in place. Trying again today.

=====

Fri, Aug 20 --- Got through the crown yesterday, pulled rods to change to NQ3 drill gear, still in BSSM

=====

Sat, Aug 21 --- no ddu

=====

Sun, Aug 22 ---slow drilling, in USMS

=====

Mon, Aug 23 --- in ACTM since 485m, going well, good intercept so far.

=====

Tue, Aug 24 --- Shut down moving this morning to set-up#9

Selwyn Project

Diamond Drill Log

Survey Data for Hole

XYC-198

<i>Depth</i>	<i>Dip</i>	<i>Azimuth</i>
0.00	-90.0	230.0
75.60	-89.7	237.6
100.00	-89.1	257.3
126.60	-89.0	246.1
150.60	-88.7	233.1
174.60	-88.0	199.7
204.00	-87.5	204.6
224.60	-87.0	187.9
273.60	-87.5	186.4
300.00	-86.5	185.0
324.60	-85.7	190.4
353.70	-85.8	196.1
375.00	-85.8	195.5
400.00	-85.0	207.4
425.00	-85.0	199.5
450.00	-85.0	209.8
476.00	-84.4	208.2
501.60	-84.4	210.9
525.00	-83.7	195.6
555.60	-83.5	205.3
561.60	-83.2	201.3

Selwyn Project Diamond Drill Log

Hole Number:
XYC-198

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
0.00	55.00	OVBR									
55.00	277.60	BSSM									
BSSM – Backside Siliceous Mudstone											
Devonian Siliceous Mudstone – Upper Chert Formation											
Greyish black laminated chert and siliceous mudstone. Randomly-oriented to bedding-parallel bioturbation is common in the bottom of the unit. « lm chrt 75.00-95.00% », « btrb 0.10-2.00cm »,											
« 55.00- 96.50 brecciated light grey siliceous mudstone with dominantly quartz as cement flt »« fault gouge 5%»« breccia 15%»« broken 50%»											
< @ 97.80 very faint beds s0 tca 50° >											
« 96.50- 111.60 calcareous mudstone with minor limestone »											
< @ 105.00 very faint beds s0 tca 41° >											
< @ 118.10 first appearance of bioturbations >											
< @ 135.80 faint parallel beds of pyrite s0 tca 45° >											
< @ 142.80 faint parallel beds of pyrite s0 tca 42° >											
< @ 148.10 parallel bioturbations s0 tca 37° >											
< @ 152.40 faint beds of pyrite s0 tca 39° >											
< @ 153.40 faint beds of pyrite s0 tca 37° >											
< @ 168.60 2mm thick chert band, parallel to faint pyrite beds s0 tca 35° >											
« 182.00- 182.80 very coarse-grained carbonate concretion »											
< @ 186.00 fine-grained pyrite bed s0 tca 65° >											
« 189.00- 222.00 light grey bioturbated interval »											
« 222.00- 226.00 laminated calcareous range »											
« 243.80- 246.30 broken zone with 10% fault gouge »											
« 250.10- 257.00 heavily broken rock with 10% thin calcite veins »											

Selwyn Project Diamond Drill Log

Hole Number:
XYC-198

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		« 270.00- 277.60 bioturbations »									
277.60	340.10	FLMD FLMD – Flaggy Mudstone Formation Dark grey mudstone in the upper portions of the unit grading into light grey mudstone to siltstone. Contains abundant wispy bioturbation which ranges from randomly-oriented at the top of the unit to bedding-parallel throughout the majority of the unit. Darker upper section has a strong fetid odour along broken surfaces. « btrb 0.10-2.00cm », « cg xtl crns ca 1.00-5.00% 5.00-150.00cm », « crns py 1.00-5.00% 0.10-0.50mm », Unit is likely shortened by fault (see below) ‹ @ 286.80 s0 tca 54° › « 292.10- 296.00 flt »« breccia 30%» ‹ @ 301.50 s0 tca 52° ›‹ @ 301.50 beta 140° › « 314.40- 317.90 flt »« breccia 20%»« fault gouge 3%» « 330.40- 334.20 major flt »« breccia 50%»« fault gouge 20%»« hydrozincite on fracture surfaces »									
340.10	349.70	FLT Major fault zone likely acts to significantly shorten Flaggy Mudstone above. The rock is primarily derived from Flaggy Mudstone, though switching to Upper Siliceous lithology. « fault »« breccia 40%»« fault gouge 15%» « 340.10- 347.50 Flaggy Mudstone rock within fault » « 347.50- 349.70 Upper Siliceous rock within fault »									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-198

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
349.70	484.60	USMS	633082	382.60	383.40	0.80	0.14	0.98	1.00	30.00	0.14
<i>USMS – Upper Siliceous Mudstone</i>			633001	383.40	384.30	0.90	0.34	7.40	6.00	170.00	0.05
<i>Consists of interlaminated dark grey to black mudstone and light to medium grey chert. Regionally, a 1m thick graptolite zone occurs 15m below the top of the upper unit, this is usable as a horizon. The USMS is divided into 3 units. The Lower Unit contains abundant limestone concretions and Galena and sphalerite micro-concretions occur locally near the base of this unit. « gra , lm chrt -20.00% », « cg xtl sph crns ca 5.00-20.00cm », « bed chrt 10.00-15.00% »,</i>			633002	384.30	384.70	0.40	0.25	5.84	5.00	130.00	0.04
			633003	384.70	385.20	0.50	0.17	1.67	3.00	50.00	0.10
			633004	385.20	385.80	0.60	0.64	11.53	7.00	260.00	0.06
			633083	385.80	386.40	0.60	0.03	0.12	1.00	5.00	0.25
			633084	396.20	396.80	0.60	0.46	3.22	3.00	90.00	0.14
			633005	396.80	397.30	0.50	2.96	15.70	8.00	390.00	0.19
			633006	397.30	397.90	0.60	3.92	10.57	9.00	310.00	0.37
			633085	397.90	398.70	0.80	0.08	0.36	1.00	10.00	0.22
			633007	481.30	482.50	1.20	0.01	0.30	1.00	10.00	0.03
			633008	482.50	483.60	1.10	0.20	0.61	2.00	20.00	0.33
« 349.70- 385.80 chert/carbonate banding visible but uncommon; concretions rare »			633009	483.60	484.60	1.00	0.41	0.32	1.00	10.00	1.28
« 355.40- 357.50 fault »« breccia 30%»« fault gouge 5%»											
< @ 358.20 calcite-rich laminations s0 tca 40° > < @ 368.70 planar, parallel series of chert bands s0 tca 44° > « 382.00- 383.40 carbonaceous fault »« breccia 30%»« gouge 20%»											
« 383.40- 384.30 laminated calcareous mudstone »											
« 384.30- 384.50 light grey laminated calcareous mineralized range; essentially active member »« 6.32% Zn »« 0.65% Pb »											
« 384.50- 384.70 fault »« breccia 75%»« 4.17 % Zn »« 0.63% Pb »											
« 385.20- 385.80 light grey laminated calcareous mudstone showing moderate visible mineralization including sph/gal nodules/stringers »« 10.86% Zn »« 3.39 % Pb »											
< @ 402.00 pyrite rich bed s0 tca 33° >											

Selwyn Project

Diamond Drill Log

Hole Number:
XYC-198

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
< @ 416.00 planar, parallel chert bands s0 tca 42° > < @ 416.00 beta 190° > < @ 425.10 s0 tca 63° > < @ 425.10 beta 80° > « 435.20- 436.70 fault »« breccia 60%»« gouge 20%» « 446.10- 448.00 fault »« breccia 30%»« gouge 10%» « 451.30- 452.60 fault »« breccia 30%»« gouge 1%» < @ 452.50 hydrozincite visible on fracture surfaces > « 459.60- 459.90 laminated mudstone with possible mineralization; NITON: 1% ZN, 1% PB » < @ 459.70 s0 tca 45° > « 467.70- 468.00 weakly laminated mudstone with faint visible mineralization; NITON: 1%Pb, Zn=nil » < @ 467.90 s0 tca 53° > « 468.80- 471.10 fault »« breccia 25%»« gouge 15%» < @ 481.10 s0 tca 47° >											
484.60	531.70	ACTM	633010	484.60	485.30	0.70	0.90	5.36	4.00	200.00	0.17
ACTM – Active Member			633011	484.60	485.30	0.70	1.08	6.52	5.00	240.00	0.17
The ACTM consists of a repetitive, possibly rhythmic, sequence of intercalated carbonaceous mudstone, cherty mudstone, chert and limestone and locally contains economically significant Zn and Pb sulphides (see bold marked facies), mainly in its sections with well developed lamination. Because of its heterogeneity, the member is distinctive and easily identified.			633012	485.30	485.90	0.60	2.61	10.98	5.00	350.00	0.24
			633013	485.90	486.60	0.70	2.59	12.58	4.00	450.00	0.21
			633014	486.60	487.40	0.80	0.51	0.50	1.00	20.00	1.02
			633015	487.40	487.90	0.50	1.64	1.94	1.00	60.00	0.85
			633016	487.90	488.40	0.50	1.76	5.40	2.00	130.00	0.33
			633017	488.40	488.90	0.50	1.03	1.45	1.00	40.00	0.71
			633018	488.90	489.20	0.30	2.53	11.80	3.00	340.00	0.21

Selwyn Project Diamond Drill Log

Hole Number:
XYC-198

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
=====			633019	489.20	490.20	1.00	5.68	18.58	1.00	900.00	0.31
The ACTM has 8 different facies:			633020	490.20	490.20	0.00	0.01	0.01	1.00	5.00	2.00
=====			633021	490.20	490.50	0.30	4.99	15.14	3.00	690.00	0.33
			633022	490.50	490.90	0.40	4.32	3.55	3.00	150.00	1.22
- GREY CHERT FACIES: Consists of laminated medium light grey to medium dark grey chert. Mineralization: 95-99% quartz and up to 5% secondary calcite.			633023	490.90	491.30	0.40	0.07	0.05	1.00	5.00	1.40
			633024	491.30	491.70	0.40	10.45	4.09	3.00	150.00	2.56
			633025	491.70	492.00	0.30	20.92	9.30	6.00	350.00	2.25
- WHITISH GREY ZN-PB MUDSTONE FACIES: Is a laminated cherty rock containing up to 70% sulphides. Mineralization: quartz, sphalerite and galena are the major minerals with only minor amounts of pyrite and locally calcite. Sedimentary diagenetic structures are common and well displayed in the facies, such as: lamination, pseudo-beds, calcite nodules & limestone nodules and abundant water escape structures. Most obvious structure in facies is cross-cutting veins containing massive sphalerite and galena with minor pyrite. They range in width from 0.5 to 10mm.			633026	492.00	493.10	1.10	1.82	0.81	1.00	30.00	2.25
			633027	493.10	493.70	0.60	0.48	2.04	1.00	80.00	0.24
			633028	493.70	494.70	1.00	0.08	0.79	1.00	20.00	0.10
			633029	494.70	495.00	0.30	0.04	0.31	1.00	5.00	0.13
			633030	495.00	495.00	0.00	0.97	1.29	221.00	90.00	0.75
			633031	495.00	495.70	0.70	0.50	1.30	1.00	30.00	0.38
			633032	495.70	496.00	0.30	2.81	18.15	4.00	490.00	0.15
			633033	496.00	496.80	0.80	1.23	1.23	1.00	40.00	1.00
			633034	496.80	498.10	1.30	0.05	0.13	1.00	5.00	0.38
- THIN BEDDED CHERTY MUDSTONE FACIES: Consists of rhythmic intercalated laminae of chert, carbonaceous mudstone and minor micrite. This facies contains significant amounts of Zn and Pb sulphides.			633035	498.10	498.80	0.70	0.01	0.04	1.00	5.00	0.25
			633036	498.80	499.30	0.50	0.17	0.33	1.00	5.00	0.52
			633037	499.30	499.80	0.50	0.04	0.23	1.00	5.00	0.17
- CHERTY MUDSTONE FACIES: Consists of a greyish black monotonous siliceous, carbonaceous mudstone. It is most typically found overlying the thin bedded calcareous mudstone facies.			633038	499.80	501.10	1.30	0.07	0.41	1.00	10.00	0.17
			633039	501.10	501.70	0.60	0.96	4.69	1.00	130.00	0.20
			633040	501.70	502.10	0.40	1.37	9.19	1.00	260.00	0.15
			633041	501.70	502.10	0.40	1.43	9.15	1.00	260.00	0.16
			633042	502.10	502.40	0.30	2.22	7.56	1.00	260.00	0.29
- THIN BEDDED CALCAREOUS MUDSTONE FACIES: Consists of laminated carbonaceous mudstone containing 20-40% calcite, 40-55% quartz and 10-20% muscovite. Sulphides occur in laminae. In the XY area it is usually the lowest facies in the section to contain laminated sulphides.			633043	502.40	503.50	1.10	0.97	3.24	1.00	100.00	0.30
			633044	503.50	504.60	1.10	1.08	4.62	1.00	120.00	0.23
			633045	504.60	505.70	1.10	0.81	3.62	1.00	90.00	0.22
			633046	505.70	506.70	1.00	0.38	2.44	1.00	60.00	0.16
			633047	506.70	507.10	0.40	2.17	1.82	1.00	50.00	1.19
- CALCAREOUS MUDSTONE FACIES: Consists of grey to greyish black monotonous, calcareous siliceous carbonaceous mudstone. There are no feathery calcite beds or pyrite-calcite blebs in the facies, making it easily distinguishable from the CCMS.			633048	507.10	508.00	0.90	1.96	5.61	1.00	150.00	0.35
			633049	508.00	509.10	1.10	1.88	8.12	1.00	250.00	0.23
			633050	509.10	509.10	0.00	0.01	0.01	1.00	5.00	2.00
			633051	509.10	509.80	0.70	2.58	5.65	1.00	160.00	0.46

Selwyn Project Diamond Drill Log

Hole Number:
XYC-198

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
- GRADED LIMESTONE FACIES: Is a laminated argillaceous limestone with intercalated carbonaceous limestone laminae. The main rock type in the facies is laminated limestone with laminae up to 0.1-7mm thick. - LIGHT GREY BASAL LIMESTONE FACIES - LGLS: Consists of laminated argillaceous limestone. In the Anniv area it marks the end of the ACTM. It's not always present in the stratigraphy. - BASAL FACIES: This is a highly contorted and locally foliated carbonaceous mudstone. Unlike the other facies it is not repeated higher in the member. It appears locally to contain the slip zone of a major slump. The facies has only been observed in the YX area. It is 0.1-2m thick. The facies consists of massive carbonaceous siliceous mudstone with lenses and laminae of contorted, slightly carbonaceous chert. AM is definitely higher grade near the top of the unit in this hole There is no visible mineralization over long stretches within the bottom half of the AM The AM here is unusually competent in this hole « 484.60- 485.90 siliceous laminated mudstone with moderate visible mineralization disseminated within laminations »« 5.7% Zn, 2.5% Pb » « 485.90- 486.60 light grey brown siliceous laminated mudstone with abundant visible mineralization »« 10.3% Zn »« 4.5% Pb » « 486.60- 487.90 light grey weakly laminated limestone with minor dark grey laminated mudstone. Some visible mineralization in mudstone. NITON: 0.8% Zn, 1.6% pb » « 487.90- 488.40 Dark grey siliceous laminated mudstone with low to moderate visible mineralization. NITON: 3.6% Zn, 1.2% Pb »			633052	509.80	510.10	0.30	1.77	5.80	1.00	220.00	0.31
			633053	510.10	510.50	0.40	3.09	12.75	2.00	400.00	0.24
			633054	510.50	511.40	0.90	0.50	0.58	1.00	20.00	0.86
			633055	511.40	512.20	0.80	0.68	0.04	1.00	5.00	17.00
			633056	512.20	512.50	0.30	0.03	0.01	1.00	5.00	6.00
			633057	512.50	512.80	0.30	1.60	2.88	1.00	100.00	0.56
			633058	512.80	513.90	1.10	0.17	0.26	1.00	5.00	0.65
			633059	513.90	514.20	0.30	2.18	3.65	1.00	130.00	0.60
			633060	514.20	514.20	0.00	1.42	4.28	29.00	270.00	0.33
			633061	514.20	515.10	0.90	1.93	5.70	1.00	160.00	0.34
			633062	515.10	515.50	0.40	6.78	23.34	7.00	690.00	0.29
			633063	515.50	516.60	1.10	4.73	14.73	4.00	400.00	0.32
			633064	516.60	517.70	1.10	6.73	27.01	6.00	760.00	0.25
			633065	517.70	518.10	0.40	0.59	1.77	1.00	40.00	0.33
			633066	518.10	518.70	0.60	0.01	0.05	1.00	5.00	0.20
			633067	518.70	519.10	0.40	0.01	0.01	1.00	5.00	2.00
			633068	519.10	520.10	1.00	0.18	0.69	1.00	20.00	0.26
			633069	520.10	521.20	1.10	0.02	0.01	1.00	5.00	4.00
			633070	521.20	521.80	0.60	0.17	0.09	1.00	5.00	1.89
			633071	521.20	521.80	0.60	0.30	0.10	1.00	5.00	3.00
			633072	521.80	522.00	0.20	4.47	0.72	14.00	20.00	6.21
			633073	522.00	523.50	1.50	0.04	0.30	1.00	10.00	0.13
			633074	523.50	524.80	1.30	0.15	0.40	1.00	20.00	0.38
			633075	524.80	525.80	1.00	0.09	0.49	1.00	20.00	0.18
			633076	525.80	527.00	1.20	0.18	1.43	3.00	50.00	0.13
			633077	527.00	528.50	1.50	0.09	0.63	2.00	30.00	0.14
			633078	528.50	529.80	1.30	0.25	0.51	3.00	20.00	0.49
			633079	529.80	530.80	1.00	0.01	0.01	1.00	5.00	2.00
			633080	530.80	530.80	0.00	0.01	0.01	1.00	5.00	2.00
			633081	530.80	531.70	0.90	0.01	0.01	1.00	5.00	2.00

Selwyn Project Diamond Drill Log

Hole Number:
XYC-198

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		« 488.40- 488.90 Light grey weakly laminated limestone NITON: 0.4% Zn, 0.7% Pb »									
		« 488.90- 489.20 Dark grey laminated siliceous mudstone with moderate visible mineralization; NITON: 6.7% Zn, 2.2% Pb »									
		« 489.20- 490.20 Lt grey strongly lam'd siliceous mdst with abundant visible min; visible SPH/GAL nodules; NITON: 18.1% Zn, 14.0 % Pb »									
		« 490.20- 490.50 As above, but with less visible mineralization; NITON: 13.1% Zn, 8.7% Pb »									
		« 490.50- 490.90 Dark grey weakly laminated siliceous mudstone with minor visible mineralization and abundant pyrite. NITON: 1.7% Zn, 2.9% Pb »									
		« 490.90- 491.30 light grey unlaminated limestone. NITON: 0.1% Zn, Pb: nil »									
		« 491.30- 491.70 Weakly laminated dark grey siliceous mudstone with visible galena crystalization including a 1cm nodule; NITON: 4.2% Zn, 2.9 % Pb »									
		« 491.70- 493.10 Light grey laminated limestone with one 4cm galena nodule. NITON: 2.3% Zn, 2.5% Pb »									
		« 493.10- 493.70 Planar laminated siliceous mudstone with low visible mineralization. Includes one unusual 2 cm thick graded sandstone bed. NITON: 0.6% Zn, 0.2% Pb »									
		« 493.70- 494.70 Unlaminatd siliceous mudstone with no visible mineralization; NITON: 0.1% Zn, 0.1% Pb »									
		« 494.70- 495.00 Light grey unlaminated limestone with minor mudstone									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-198

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		clasts (angular contacts) NITON: 0.2% Zn, Pb=nil » « 495.00- 495.70 unlaminated siliceous mudstone; broken; no visible mineralization; NITON: 0.6% Zn, 0.1% Pb » « 495.70- 496.00 Strongly lam'd lt brown siliceous mdst w strong mineralization disseminated; inc's minor interbedded limestone clasts; NITON : 11.3% Zn, 3.5% Pb » « 496.00- 499.30 Light grey limestone weakly laminated, with minor interbedded calcareous mudstone; no visible mineralization; NITON: 0.4% Zn, 0.3% Pb » « 499.30- 499.80 Unlaminated siliceous mudstone with cherty texture. NO visible mineralization; NITON: 0.2% Zn, Pb = Nil » « 499.80- 501.10 light grey weakly laminated limestone; NITON: 0.4% Zn, 0.1% Pb » « 501.10- 501.70 Weakly laminated calcareous mudstone; broken; weak visible mineralization; NITON: 2.5% Zn, 1.2 % Pb » « 501.70- 502.10 Light grey calcareous mudstone laminated with complex structure and strong visible min. NITON: 6.4% Zn, 2.3% Pb » « 502.10- 502.40 Calc mdst partially lam'd with moderate visible mineralization; includes a 5 cm light grey laminated mineralized section; NITON: 3.7 %Zn, 2.2%Pb » « 502.40- 504.60 Limestone, both light and dark grey, interbedded with minor mudstone, locally laminated; weak visible mineralization; NITON: 2.4% Zn, 1.2% Pb » « 504.60- 506.70 Weakly calcareous , weakly laminated dark grey mudstone									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-198

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		with weak visible disseminated mineralization; NITON: 1.3% Zn, 1.9% Pb »									
		« 506.70- 507.10 Light grey limestone with weakly laminated mudstone and low visible mineralization; NITON: 1.7% Zn, 2.1 % Pb »									
		« 507.10- 509.80 Weakly laminated clacareous mudstone with minor interbedded limestone and weak visible mineralization; NITON: 3.5% Zn, 1.6% Pb »									
		« 509.80- 510.10 laminated limestone; NITON: 4.5% Zn, 3.6% Pb »									
		« 510.10- 510.50 Strongly laminated calcareous mudstone with moderate visible mineralization; NITON: 8.4% Zn, 4.6% Pb »									
		« 510.50- 511.40 Unlaminated calcareous mudstone with minor limestone concretions and no visible mineralization; NITON: Zn: nil; Pb: 0.3% »									
		« 511.40- 512.20 Light grey limestone; NITON: Zn: nil; Pb: 0.3% »									
		« 512.20- 512.50 calcareous mudstone unlaminated; NITON: Zn: nil; Pb: 0.1% »									
		« 512.50- 512.80 light grey limestone; NITON: 2.4% Zn, 1.2% Pb »									
		« 512.80- 513.90 unlaminated calcareous mudstone with 30% limestone and no visible mineralization; NITON: 0.2% Zn, 0.2% Pb »									
		« 513.90- 514.20 laminated, weakly calcareous mudstone with weak visible mineralization; NITON: 2.6% Zn, 2.0 % Pb »									
		« 514.20- 515.10 weakly laminated, weakly calcareous mudstone with low visible mineralization; NITON: 1.6% Zn, 1.2% Pb »									
		« 515.10- 517.70 Light grey laminated siliceous mudstone with strong visible mineralization throughout; NITON: 13.5% Zn, 6.9% Pb »									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-198

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		« 517.70- 520.10 weakly lam'd sil mdst w lg (40cm app. thickness) cal vein & minor limestone; weak visible mineralization; NITON: 0.1% Zn, 0.1% Pb » « 519.10- 520.10 unlaminated calcareous mudstone with no visible mineralization; NITON: 0.5% Zn, 0.3% Pb » « 520.10- 521.20 laminated limestone; NITON: Zn: nil, Pb: 0.1% » « 521.20- 521.80 Dark grey unlaminated siliceous mudstone; NITON: 0.1% Zn, 0.3% Pb » « 521.80- 522.00 Light grey limestone; NITON: 0.2% Zn, 1.9% Pb » « 522.00- 523.50 Siliceous, unlaminated mudstone; NITON: 0.1% Zn, 0.3% Pb » « 523.50- 525.80 medium grey unlaminated limestone; NITON: 0.2% Zn, 0.1% Pb » « 525.80- 529.80 Locally calcareous mudstone locally bedded by pyrite and calcite-rich beds; NITON: 0.4% Zn, 0.2% Pb » < @ 528.00 pyrite-rich bed - in active member but looks good s0 tca 48° > @ 525.80 beta 150° > « 529.80- 531.70 LIght grey unlaminated basal limestone facies; NITON: 0.1% Zn, Pb: nil »									
531.70	561.60	CCMS									
CCMS – Calcareous Mudstone											
Massive, calcareous, carbonaceous, dark grey mudstone. Most of the member is massive, but rare poorly defined bedding and pyrite-calcite micro-concretions											

Selwyn Project Diamond Drill Log

Hole Number:
XYC-198

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		are present. Most diagnostic structures are feathery calcite beds (=thin calcite-cemented concretions, many of them contain pyrite cores) and calcite pseudo-beds (= fibrous calcite vein parallel to bedding).									
		« lm ca 5.00-10.00mm », « nodules py -3.00% 2.00-20.00mm », < @ 533.50 s0 tca 64° > @ 533.50 beta 160° >									
		« 539.30- 539.60 fault »« breccia 40%»« gouge 20%»									
		< @ 557.20 s0 tca 46° >									
561.60	561.60	EOH									

Diamond Drill Log

Comprehensive Report for Hole:

XYC-197

Hole No.: XYC-197	Depth: 313.20 m	Horizontal Length: 0.00 m	Project: 1710
Location Data:			
Property:	Selwyn Project	Claim Name:	X 2
Mining District:	Selwyn Basin	Grant Number:	Y 64527
Province/Territory:	Yukon		
UTM Co-Ordinates & Altitude of Drill Hole Collar:			
UTM Easting:	488296.24 m	True Azimuth:	193.0 °
UTM Northing:	6926778.46 m	Hole Angle:	-77.5 °
Elevation (m):	1576.29 m	NTS Name:	Placer Creek
		UTM Datum:	NAD 83
		UTM Grid Zone:	9
		NTS Number:	105I06
Grid Co-Ordinates of Drill Hole Collar:			
Grid Easting (m):	0.00 m	Grid Name:	HP 06
Grid Northing (m):	0.00 m	Grid Type:	100m
Grid Azimuth:	253.0 °		
Dimond Drilling Contract:			
Drilled By:	NL-01	Date Drilling Start:	08/03/2010
		Date Finish:	08/10/2010
Diamond Drill Core:			
Logged By:	Jelle De Bruyckere	Date Logging Start:	08/08/2010
		Date Finish:	08/14/2010
Legend for Core Logging Codes: PAX			
Core Size:	NQ3	Cemented:	Yes
Casing Depth:	16.70 m	Casing Pulled:	Yes
Water Depth:	0.00 m	Overburden Depth:	16.70 m
Level:	Section:	Drift:	

Selwyn Project

Diamond Drill Log

Survey Data for Hole

XYC-197

Hole Comments:

Wed, Aug 04 --- The NL-01 drill got moved to setup #31 yesterday morning. 55' of casing was put in. At morning shift change the total depth was at 24.4m (80'). The core seems to be FLMD. Only one box of core, about half is pebbles and broken pieces of core. Bioturbated mudstone visible. They used 2 diamond bits to drill 25' in the past 12hrs.

=====

Thu, Aug 05 ---In BSSM at a total depth of 77.4m. Locally short stretches of bioturbations. Pyrite concretions and carbonate concretions occur too. Drilling is going well, no mechanical problems to mention.

=====

Fri, Aug 06 --- Possibly in FLMD at a total depth of 124m. If indeed FLMD, then the BSSM-FLMD contact is approximately at 98.5m. Core is rather competent, with locally some brco + minor flt gg.

=====

Sat, Aug 07 --- Still in FLMD, at a total depth of 210m. Core is very competent. No mechanical problems to mention. Drilling is going really well, 86m in the past 24hrs.

=====

Sun, Aug 08 ---In USMS at a total depth of 248.4m. The FLMD-USMS contact was exactly at 207.6m. A fault was encountered at 211.8m and is still ongoing.

=====

Mon, Aug 09 --- In ACTM at a total depth of 281m. The USMS-ACTM contact was approximately at 255m. Fairly competent core.

=====

Tue, Aug 10 ---In CCMS at a total depth of 313m. The hole got shut down this morning. Today's dayshift will cement the hole before moving onto the new setup, #1.

<i>Depth</i>	<i>Dip</i>	<i>Azimuth</i>
0.00	-77.5	193.0
24.40	-77.3	191.6
48.50	-77.5	189.8
73.20	-76.9	190.1
97.50	-75.6	191.8
121.90	-75.1	193.2
146.30	-74.8	196.1
170.70	-74.5	194.8
195.10	-74.1	195.6
218.50	-73.8	197.4
243.80	-73.8	198.0
267.90	-72.9	194.7
291.40	-72.9	196.6

Selwyn Project Diamond Drill Log

Hole Number:
XYC-197

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
0.00	16.70	OVBR									
16.70	141.00	BSSM									
<i>BSSM – Backside Siliceous Mudstone</i> <i>Greyish siliceous mudstone. Randomly-oriented to bedding-parallel bioturbation is common in the bottom of the unit. « lm chrt 75.00-95.00% », « btrb 0.10-2.00cm »</i> <i>« Classic BSSM in the vicinity of FLMD, with plenty of short to middle long bioturbated sections, pyrite (concretions, bands, beds), chert bands/nodules and carbonate concretions.»</i> <i>« 16.70- 21.20 Broken core due to weathering. Within this section there is an 80cm long piece of carbonate. »</i> <i>< @ 34.60 S0 defined by a 2 mm chert band - S0 tca 49° ></i> <i>< @ 35.70 S0 defined by a 2mm chert band, parallel to bioturbations and parallel to a calcite pseudo-bed - S0 tca 60° ></i> <i>< @ 38.80 S0 defined by parallel elongated pyrite bands - S0 tca 50° ></i> <i>« 42.10- 45.70 Section consists mainly of a breccia of siliceous mudstone fragments in a calcite matrix. »</i> <i>< @ 54.00 S0 defined by a faint bed - S0 tca 55° ></i> <i>< @ 58.80 S0 defined by a calcite pseudo-bed - S0 tca 32° ></i> <i>Note: Even though calcite pseudo-beds usually appear only in CCMS, I am pretty confident that both calcite pseudo-beds mentioned above are indeed parallel to S0.</i> <i>< @ 76.80 S0 defined by faint beds - S0 tca 34° ></i>											

Selwyn Project Diamond Drill Log

Hole Number:
XYC-197

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		< @ 84.10 S0 defined by bioturbations - S0 tca 39° > < @ 90.30 S0 defined by thin beds - S0 tca 32° > < @ 102.00 S0 defined by bioturbations - S0 tca 58° > « 101.30- 115.10 Section of FLMD appearing core: light grey siliceous mudstone, continuously bioturbated) » < @ 107.10 S0 defined by bioturbations - S0 tca 30° > < @ 110.20 S0 defined by bioturbations - S0 tca 52° > < @ 126.80 S0 defined by bioturbations - S0 tca 58° > < @ 135.70 S0 defined by bioturbations - S0 tca 60° >									
141.00	208.90	FLMD									
		FLMD – Flaggy Mudstone Formation Dark grey mudstone in the upper portions of the unit grading into light grey mudstone to siltstone. Contains abundant wispy bioturbation which ranges from randomly-oriented at the top of the unit to bedding-parallel throughout the majority of the unit. Darker upper section has a strong fetid odour along broken surfaces. « btrb 0.10-2.00cm », « cg xtl crns ca 1.00-5.00% 5.00-150.00cm », « crns py 1.00-5.00% 0.10-0.50mm » « 141.00- 208.90 Classic FLMD. Light grey, siliceous mudstone. Continuously bioturbated; pyrite (as nodules, concretions and disseminated) often with calcite rims. » < @ 141.90 S0 defined by bioturbations - S0 tca 66° > < @ 143.60 S0 defined by bioturbations - S0 tca 64° > < @ 144.40 S0 defined by bioturbations - S0 tca 67° > < @ 152.90 S0 defined by bioturbations - S0 tca 58° > < @ 152.90 Beta 178° > < @ 160.20 S0 defined by bioturbations - S0 tca 60° > < @ 175.30 S0 defined by bioturbations - S0 tca 60° > < @ 175.30 Beta 167° > < @ 184.50 S0 defined by bioturbations - S0 tca 26° > < @ 186.70 S0 defined by bioturbations - S0 tca 30° >									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-197

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		« 206.10- 207.60 Breccia, consisting of siliceous mudstone, with quartz as cement. This breccia is part of the fault that's described in the next unit. »									
208.90	255.00	USMS	631801	250.80	252.00	1.20	0.04	0.06	1.00	5.00	0.67
		USMS – Upper Siliceous Mudstone	631802	252.00	255.00	3.00	0.05	1.29	1.00	50.00	0.04
		Consists of interlaminated dark grey to black mudstone and light to medium grey chert. Regionally, a 1m thick graptolite zone occurs 15m below the top of the upper unit, this is usable as a horizon. The USMS is divided into 3 units. The Lower Unit contains abundant limestone concretions and Galena and sphalerite micro-concretions occur locally near the base of this unit. « gra , lm chrt -20.00% », « cg xtl sph crns ca 5.00-20.00cm », « bed chrt 10.00-15.00% »									
		« 208.90- 255.00 Classic USMS, but strongly faulted. »« flt gg 20%»« flt bx 15%»« brco 50°»« competent core 15%»									
		« @ 218.90 S0 defined by parallel chert bands - S0 tca 56° »									
255.00	278.60	ACTM	631803	255.00	255.40	0.40	0.08	0.18	4.00	5.00	0.44
		ACTM – Active Member	631804	255.40	256.10	0.70	3.53	9.05	4.00	440.00	0.39
		The ACTM consists of a repetitive, possibly rhythmic, sequence of intercalated carbonaceous mudstone, cherty mudstone, chert and limestone and locally contains economically significant Zn and Pb sulphides (see bold marked facies), mainly in its sections with well developed lamination. Because of its heterogeneity, the member is distinctive and easily identified.	631805	256.10	256.90	0.80	1.13	6.48	5.00	180.00	0.17
			631806	256.90	257.80	0.90	2.18	6.32	1.00	150.00	0.34
			631807	257.80	258.60	0.80	1.43	5.24	1.00	130.00	0.27
			631808	258.60	259.40	0.80	0.93	3.05	1.00	80.00	0.30
			631809	259.40	259.80	0.40	0.05	0.45	1.00	10.00	0.11
			631810	259.80	261.20	1.40	0.09	0.42	1.00	10.00	0.21
			631811	259.80	261.20	1.40	0.27	0.65	1.00	20.00	0.42
			631812	261.20	262.40	1.20	0.16	1.01	1.00	30.00	0.16
		=====	631813	262.40	262.90	0.50	2.57	15.46	3.00	390.00	0.17
		The ACTM has 8 different facies:	631814	262.90	264.30	1.40	1.85	1.60	1.00	50.00	1.16
		=====	631815	264.30	265.40	1.10	2.01	7.87	1.00	220.00	0.26
		- GREY CHERT FACIES: Consists of laminated medium light grey to medium dark	631816	265.40	265.90	0.50	1.40	2.94	1.00	90.00	0.48

Selwyn Project Diamond Drill Log

Hole Number:
XYC-197

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
grey chert. Mineralization: 95-99% quartz and up to 5% secondary calcite. - WHITISH GREY ZN-PB MUDSTONE FACIES: Is a laminated cherty rock containing up to 70% sulphides. Mineralization: quartz, sphalerite and galena are the major minerals with only minor amounts of pyrite and locally calcite. Sedimentary diagenetic structures are common and well displayed in the facies, such as: lamination, pseudo-beds, calcite nodules & limestone nodules and abundant water escape structures. Most obvious structure in facies is cross-cutting veins containing massive sphalerite and galena with minor pyrite. They range in width from 0.5 to 10mm. - THIN BEDDED CHERTY MUDSTONE FACIES: Consists of rhythmic intercalated laminae of chert, carbonaceous mudstone and minor micrite. This facies contains significant amounts of Zn and Pb sulphides. - CHERTY MUDSTONE FACIES: Consists of a greyish black monotonous siliceous, carbonaceous mudstone. It is most typically found overlying the thin bedded calcareous mudstone facies. - THIN BEDDED CALCAREOUS MUDSTONE FACIES: Consists of laminated carbonaceous mudstone containing 20-40% calcite, 40-55% quartz and 10-20% muscovite. Sulphides occur in laminae. In the XY area it is usually the lowest facies in the section to contain laminated sulphides. - CALCAREOUS MUDSTONE FACIES: Consists of grey to greyish black monotonous, calcareous siliceous carbonaceous mudstone. There are no feathery calcite beds or pyrite-calcite blebs in the facies, making it easily distinguishable from the CCMS. - GRADED LIMESTONE FACIES: Is a laminated argillaceous limestone with intercalated carbonaceous limestone laminae. The main rock type in the facies is laminated limestone with laminae up to 0.1-7mm thick.			631817	265.90	266.90	1.00	0.29	1.19	1.00	30.00	0.24
			631818	266.90	267.10	0.20	0.83	3.73	1.00	100.00	0.22
			631819	267.10	267.30	0.20	2.35	4.50	1.00	110.00	0.52
			631820	267.30	267.30	0.00	0.01	0.01	1.00	5.00	2.00
			631821	267.30	267.70	0.40	4.51	14.38	2.00	520.00	0.31
			631822	267.70	269.10	1.40	3.08	11.55	3.00	330.00	0.27
			631823	269.10	269.80	0.70	2.97	9.29	3.00	270.00	0.32
			631824	269.80	270.70	0.90	0.68	0.11	1.00	5.00	6.18
			631825	270.70	271.90	1.20	0.05	0.07	1.00	5.00	0.71
			631826	271.90	273.10	1.20	1.19	0.89	1.00	30.00	1.34
			631827	273.10	274.10	1.00	0.01	0.09	1.00	5.00	0.11
			631828	274.10	275.70	1.60	0.01	0.05	1.00	5.00	0.20
			631829	275.70	276.30	0.60	0.24	1.50	1.00	30.00	0.16
			631830	276.30	276.30	0.00	6.11	7.07	70.00	190.00	0.86
			631831	276.30	277.80	1.50	0.25	0.62	1.00	20.00	0.40
			631832	277.80	278.60	0.80	0.03	0.07	1.00	5.00	0.43

Selwyn Project Diamond Drill Log

Hole Number:
XYC-197

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		- LIGHT GREY BASAL LIMESTONE FACIES - LGLS: Consists of laminated argillaceous limestone. In the Anniv area it marks the end of the ACTM. It's not always present in the stratigraphy. - BASAL FACIES: This is a highly contorted and locally foliated carbonaceous mudstone. Unlike the other facies it is not repeated higher in the member. It appears locally to contain the slip zone of a major slump. The facies has only been observed in the YX area. It is 0.1-2m thick. The facies consists of massive carbonaceous siliceous mudstone with lenses and laminae of contorted, slightly carbonaceous chert. « 255.00- 255.40 Siliceous mudstone with minor pyrite. No visible sphalerite of galena. Faint mineralization: 0.6% Zn & 0.0% Pb. » « 255.40- 256.10 Whitish Grey Zn-Pb Mudstone Facies. Mineralization: 9.0% Zn & 8.0% Pb. » « 256.10- 257.80 Siliceous mudstone. Roughly 60% is broken up. Majority of the core shows moderately developed lamination. Mineralization: 4.2% Zn & 2.0% Pb. » « 257.80- 259.40 This range consists of alternating sections of calcareous or siliceous mudstone (generally with a well developed lamination) and limestone clasts. Mineralization: 3.4% Zn & 1.3% Pb. » « 259.40- 259.80 Very calcareous mudstone with a moderately developed lamination. Faint mineralization: 0.6% Zn & 0.0% Pb. » « 259.80- 262.40 Siliceous carbonaceous mudstone with no visible mineralization. Faint mineralization: 0.6% Zn & 0.6% Pb. » « 262.40- 262.90 Siliceous mudstone with a well developed lamination. Fairly rich in pyrite. Mineralization: 10.3% Zn & 3.3% Pb. »									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-197

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		« 262.90- 264.30 Mainly limestone. Consists also of calcareous mudstone with minor sphalerite+galena+pyrite. Mineralization: 1.1% Zn & 1.0% Pb. »									
		« 264.30- 265.40 Siliceous carbonaceous mudstone with a well developed lamination. Mineralization: 4.8% Zn & 2.2% Pb. »									
		« 265.40- 265.90 Badly broken up section. About 60% is flt bx. Poor recovery. Mineralization: 11% Zn & 6% Pb. »									
		« 265.90- 266.90 Mainly limestone or very calcareous mudstone. Mineralization: 1.2% Zn & 0.5% Pb. »									
		« 266.90- 267.10 Breccia of slightly calcareous mudstone. Mineralization: 3.0% Zn & 1.0% Pb. »									
		« 267.10- 267.30 Very calcareous mudstone with limestone clasts. Mineralization: 0.8% Zn & 1.1% Pb. »									
		« 267.30- 267.70 Moderately developed lamination. Visible sphalerite + galena. High Grade. Mineralization: 16% Zn & 14% Pb. »									
		« 267.70- 269.80 About half of this section has very well developed lamination. The other half moderately developed lamination. Visible sphalerite crystals and galena stringers & blebs. Mineralization: 8.0% Zn & 4% Pb. »									
		« 269.80- 271.90 Barren section. Very calcareous mudstone with limestone clasts and calcite veining. »									
		« 271.90- 274.10 Partially siliceous, partially calcareous carbonaceous mudstone. Locally contorted. Limestone clasts are present. Mineralization 1.0% Zn & 1.0% Pb. »									
		« 274.10- 275.70 Barren. Graded Limestone Facies. »									
		« 275.70- 276.30 Slightly calcareous mudstone. No visible									

Selwyn Project

Diamond Drill Log

Hole Number:
XYC-197

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		mineralization. Faint mineralization: 0.5% Zn & 0.3% Pb. » « 276.30- 277.80 Calcareous mudstone with limestone clasts. No visible mineralization. Faint mineralization: 1.0% Zn & 0.3 % Pb. » « 277.80- 278.60 Basal Light Grey Limestone »									
278.60	313.20	CCMS	631833	278.60	280.00	1.40	0.28	1.07	3.00	40.00	0.26
		CCMS – Calcareous Mudstone Massive, calcareous, carbonaceous, dark grey mudstone. Most of the member is massive, but rare poorly defined bedding and pyrite-calcite micro-concretions are present. Most diagnostic structures are feathery calcite beds (=thin calcite-cemented concretions, many of them contain pyrite cores) and calcite pseudo-beds (= fibrous calcite vein parallel to bedding). « lm ca 5.00-10.00mm », « nodules py -3.00% 2.00-20.00mm » « 278.60- 313.20 Classic CCMS. Fairly broken up. » ◁ @ 286.90 S0 defined by faint beds S0 tca 69° ▷ ◁ @ 288.40 S0 defined by faint beds S0 tca 75° ▷ ◁ @ 304.60 S0 defined by faint beds S0 tca 65° ▷									
313.20	313.20	EOH									

Diamond Drill Log

Comprehensive Report for Hole:

XYC-196

Hole No.: XYC-196	Depth: 579.70 m	Horizontal Length: 0.00 m	Project: 1710
Location Data:			
Property:	Selwyn Project	Claim Name:	X 2
Mining District:	Selwyn Basin	Grant Number:	Y 64527
Province/Territory:	Yukon		
UTM Co-Ordinates & Altitude of Drill Hole Collar:			
UTM Easting:	488488.37 m	True Azimuth:	50.0 °
UTM Northing:	6926813.20 m	Hole Angle:	-85.0 °
Elevation (m):	1645.89 m	NTS Name:	Placer Creek
		NTS Number:	105I06
Grid Co-Ordinates of Drill Hole Collar:			
Grid Easting (m):	0.00 m	Grid Name:	HP 06
Grid Northing (m):	0.00 m	Grid Type:	100m
Grid Azimuth:	110.0 °		
Dimond Drilling Contract:			
Drilled By:	NL-02	Date Drilling Start:	07/29/2010
		Date Finish:	08/09/2010
Diamond Drill Core:			
Logged By:	Matthew Jodrey	Date Logging Start:	08/05/2010
		Date Finish:	08/10/2010
Legend for Core Logging Codes: PAX			
Core Size:	NQ3	Cemented:	Yes
Casing Depth:	21.00 m	Casing Pulled:	Yes
Water Depth:	0.00 m	Overburden Depth:	21.00 m
Level:			
Section:		Drift:	

Selwyn Project

Diamond Drill Log

Survey Data for Hole

XYC-196

Hole Comments:

Fri, Jul 30 --- Shut down XYC-194 after day shift in CCMS at 309.7 meters. Moved NL-02 last night to XYC-196 (setup # 29) NS started putting down casing last night and drilling will begin this morning.

Sat, Jul 31 --- In BSSM at a total depth of 75.7m. The DeviCore extension had to be replaced yesterday afternoon, because they dropped the innertube. Apparently the lifterdogs were damaged before that when they were trying to retrieve the packer tester.

Sun, Aug 01 --- Still in BSSM at a total depth of 165.7m. Competent core. Drilling is going really well.

Mon, Aug 02 --- Still in competent BSSM at a total depth of 207.7m.

Tue, Aug 03 --- Still in fairly competent BSSM. The first locally bioturbated sections appeared in the core.

Wed, Aug 04 --- Still in BSSM at a total depth of 310.2m. Less competent core. Broken core and flt gg from 304.2m to 307.8m.

Thu, Aug 05 --- In FLMD now, at a total depth of 366.7m. Core is rather competent, a bit broken up from 360.5m to 366.7m, with minor flt gg.

Fri, Aug 06 --- Still in FLMD at morning shift change. Total depth is at 426.7m. Core is very competent.

Sat, Aug 07 --- Still FLMD this morning. After drilling 48m in the past 24hrs, the total depth of the hole is now 474.7m. Core is competent, 1m stretch of broken core around 465.7m.

Sun, Aug 08 --- In USMS at a total depth of 525.7m. The FLMD-USMS contact was roughly at 505m. Core still competent.

Mon, Aug 09 --- At morning shift change the total depth was 567.7m. We're in footwall rocks now. After the FLMD, we only saw about 12m of USMS. Then the 40cm mineralized section encountered in yesterday's core at 517m was actually ACTM, and not a mineralized stretch within USMS. It seems that those 40cm was the only mineralized core in ACTM, followed by a few meters of barren ACTM, before going into footwall rock. David wants to go another 15m hoping to hit a fault with possibly another ACTM lens.

Tue, Aug 10 --- XYC-196 got shut down at 579.7m, just before lunchtime. The drill got moved to #19 late afternoon and was lined up around in the early evening; note that the AZI is 230, and DIP is -87 as per JJ changes on Friday Aug 6th. Last night 69' of casing was put in place in XYC-198.

Selwyn Project

Diamond Drill Log

Survey Data for Hole

XYC-196

<i>Depth</i>	<i>Dip</i>	<i>Azimuth</i>
0.00	-85.0	50.0
51.70	-84.5	46.6
75.70	-84.3	41.1
100.00	-84.1	46.4
126.00	-83.8	48.0
150.70	-84.2	54.3
176.00	-84.5	58.1
201.70	-84.0	54.9
227.00	-83.8	62.3
250.00	-83.6	58.6
276.00	-83.7	60.9
300.70	-83.4	63.0
325.00	-83.3	63.4
351.70	-83.6	65.9
375.00	-83.4	64.3
399.00	-82.9	64.7
426.70	-82.3	64.2
450.00	-81.4	62.8
475.00	-80.5	61.9
499.00	-80.4	60.7
525.70	-80.5	64.0
550.00	-80.5	68.7
580.00	-80.8	71.6

Selwyn Project Diamond Drill Log

Hole Number:
XYC-196

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
0.00	21.00	OVBR									
21.00	331.60	BSSM									
<i>BSSM – Backside Siliceous Mudstone</i> <i>Devonian Siliceous Mudstone – Upper Chert Formation</i> <i>Greyish black laminated chert and siliceous mudstone. Randomly-oriented to bedding-parallel bioturbation is common in the bottom of the unit. Includes limestone concretions locally; « lm chrt 75.00-95.00% », « btrb 0.10-2.00cm »,</i> <i>« 21.00- 32.10 highly fractured and broken up »</i> <i>< @ 32.30 carbonaceous bed s0 tca 46° ></i> <i>< @ 43.40 carbonaceous bed s0 tca 54° ></i> <i>« 60.70- 67.90 lighter grey range; includes first appearance of bioturbations »</i> <i>« 74.10- 77.70 flt »</i> <i>< @ 84.80 carbonaceous bed s0 tca 60° ></i> <i>« 96.50- 104.80 strongly fractured »</i> <i>< @ 105.90 carbonaceous bed s0 tca 63° ></i> <i>« 110.10- 122.80 light grey bioturbated range »</i> <i>< @ 116.80 carbonaceous bed s0 tca 55° ></i> <i>< @ 130.50 compositional banding s0 tca 51° ></i>											

Selwyn Project Diamond Drill Log

Hole Number:
XYC-196

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		< @ 152.30 compositional banding (thin laminations) s0 tca 50° > « 163.00- 211.80 range includes thin, lenticular, nodules of very fine grained pyrite/qtz, along bedding; PSMS-like feature often observed in BSSM » < @ 163.10 pyrite-rich 1cm bed s0 tca 60° > < @ 166.80 lenticular pyrite nodules and carbonaceous bed s0 tca 70° > < @ 177.20 lenticular parallel pyrite nodules s0 tca 35° > < @ 200.00 pyrite-rich laminations and pyrite-rich lenticular concretions s0 tca 60° > « 205.20- 211.80 strongly laminated, with laminations defined by fine-grained quartz/pyrite (0.1-10 mm thickness) » < @ 208.40 compositional lamination s0 tca 67° > < @ 225.50 quartz-rich bed s0 tca 70° > < @ 234.90 compositional lamination s0 tca 67° > < @ 245.40 compositional lamination s0 tca 54° > < @ 254.80 plane of compositional change s0 tca 53° > « 259.50- 278.90 light grey bioturbated » < @ 284.40 compositional laminations s0 tca 50° > < @ 295.50 pyrite-rich laminations s0 tca 40° > < @ 310.40 compositional laminations s0 tca 33° >									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-196

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
< @ 320.40 pyrite-rich laminations s0 tca 43° >											
331.60	505.90	FLMD									
FLMD – Flaggy Mudstone Formation											
Dark grey mudstone in the upper portions of the unit grading into light grey mudstone to siltstone. Contains abundant wispy bioturbation which ranges from randomly-oriented at the top of the unit to bedding-parallel throughout the majority of the unit. Darker upper section has a strong fetid odour along broken surfaces. « btrb 0.10-2.00cm », « cg xtl crns ca 1.00-5.00% 5.00-150.00cm », « crns py 1.00-5.00% 0.10-0.50mm »,											
< @ 355.90 compositional lamination s0 tca 30° >											
« 360.20- 375.00 strongly fractured range »											
< @ 373.40 carbonaceous bed s0 tca 43° >											
< @ 389.80 carbonaceous bed s0 tca 55° >											
< @ 397.00 carbonaceous bed s0 tca 50° >											
< @ 405.70 carbonaceous bed s0 tca 44° >											
« 417.00- 430.80 medium-dark grey mudstone with limestone; weakly bioturbated locally; variably calcareous »											
< @ 423.20 carbonaceous bed s0 tca 57° >											
« 425.00- 428.20 dark grey limestone or strongly calcareous mudstone; laminated locally; gradational contacts on top and bottom - ie, not a concretion »											
< @ 447.90 carbonaceous bed s0 tca 43° > < @ 447.90 beta 153° >											
< @ 450.30 carbonaceous bed s0 tca 40° > < @ 450.30 beta 180° >											

Selwyn Project Diamond Drill Log

Hole Number:
XYC-196

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		« 464.00- 481.10 medium grey, weakly bioturbated » < @ 474.60 carbonaceous bed s0 tca 52° > < @ 474.60 beta 230° > < @ 490.90 s0 tca 30° > < @ 492.90 carbonaceous bed s0 tca 36° > < @ 492.90 11 degree variance beta 275° >									
505.90	520.90	USMS	632151	515.70	516.60	0.90	0.02	0.22	1.00	20.00	0.09
USMS – Upper Siliceous Mudstone			632152	516.60	517.00	0.40	0.36	4.30	4.00	150.00	0.08
Consists of interlaminated dark grey to black mudstone and light to medium grey chert. Regionally, a 1m thick graptolite zone occurs 15m below the top of the upper unit, this is usable as a horizon. The USMS is divided into 3 units. The Lower Unit contains abundant limestone concretions and Galena and sphalerite micro-concretions occur locally near the base of this unit. Unit is shortened, likely due to fault (see below). Lithology is typical and core is generally competent. « gra , lm chrt -20.00% », « cg xtl sph crns ca 5.00-20.00cm », « bed chrt 10.00-15.00% », « 505.90- 511.30 heavily fractured, with polished, graphitic fracture surfaces; heavy calcite veining throughout » « 511.30- 517.00 typical USMS with abundant chert/carbonate banding » < @ 513.70 s0 tca 40° > « 517.00- 517.50 mineralized range; active member-like; lt grey lam'd wk calc mdst w minr visible gal veinlettes & minor visible sph nodules » « 517.00- 517.50 12% zinc »« 4% lead »			632153	517.00	517.50	0.50	1.49	16.06	11.00	560.00	0.09
			632154	517.50	517.80	0.30	0.10	0.26	1.00	5.00	0.38
			632155	517.80	518.90	1.10	0.01	0.21	1.00	20.00	0.05
			632156	518.90	520.00	1.10	0.01	0.01	1.00	5.00	2.00

Selwyn Project Diamond Drill Log

Hole Number:
XYC-196

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
< @ 518.50 s0 tca 25° >											
			632157	520.00	521.10	1.10	0.01	0.01	1.00	5.00	2.00
520.90	522.70	FLT	632158	521.10	522.10	1.00	0.01	0.01	1.00	20.00	2.00
<i>This fault zone likely shortens the Upper Siliceous above and cut out most of the Active Member below. Before this fault zone the rock is clearly Upper Siliceous, and afterward exhibits features of mixed Active Member and Calcareous Mudstone. There is a spike in Niton zinc readings after this fault zone. The fault zone is rather narrow, but this seems the most likely explanation based on observations.</i> « 520.90- 522.40 Generally competent core but extremely veined with graphitic, polished fracture surfaces and a possibly reconstituted appearance flt » « 522.40- 522.70 flt »« breccia 99%»			632159	522.10	522.70	0.60	0.01	0.02	1.00	20.00	0.50
522.70	528.40	ACTM	632160	522.70	523.50	0.80	0.01	1.05	2.00	60.00	0.01
ACTM – Active Member <i>The ACTM consists of a repetitive, possibly rhythmic, sequence of intercalated carbonaceous mudstone, cherty mudstone, chert and limestone and locally contains economically significant Zn and Pb sulphides (see bold marked facies), mainly in its sections with well developed lamination. Because of its heterogeneity, the member is distinctive and easily identified.</i> ===== <i>The ACTM has 8 different facies:</i> ===== - GREY CHERT FACIES: Consists of laminated medium light grey to medium dark grey chert. Mineralization: 95-99% quartz and up to 5% secondary calcite. - WHITISH GREY ZN-PB MUDSTONE FACIES: Is a laminated cherty rock containing			632161	522.70	523.50	0.80	0.01	0.91	1.00	60.00	0.01
			632162	523.50	524.20	0.70	0.01	0.02	1.00	20.00	0.50
			632163	524.20	525.20	1.00	0.06	0.37	2.00	10.00	0.16
			632164	525.20	526.30	1.10	0.03	0.55	2.00	40.00	0.05
			632165	526.30	527.30	1.00	0.02	0.11	2.00	30.00	0.18
			632166	527.30	528.40	1.10	0.01	0.01	1.00	20.00	2.00

Selwyn Project Diamond Drill Log

Hole Number:
XYC-196

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		up to 70% sulphides. Mineralization: quartz, sphalerite and galena are the major minerals with only minor amounts of pyrite and locally calcite. Sedimentary diagenetic structures are common and well displayed in the facies, such as: lamination, pseudo-beds, calcite nodules & limestone nodules and abundant water escape structures. Most obvious structure in facies is cross-cutting veins containing massive sphalerite and galena with minor pyrite. They range in width from 0.5 to 10mm. - <i>THIN BEDDED CHERTY MUDSTONE FACIES:</i> Consists of rhythmic intercalated laminae of chert, carbonaceous mudstone and minor micrite. This facies contains significant amounts of Zn and Pb sulphides. - <i>CHERTY MUDSTONE FACIES:</i> Consists of a greyish black monotonous siliceous, carbonaceous mudstone. It is most typically found overlying the thin bedded calcareous mudstone facies. - <i>THIN BEDDED CALCAREOUS MUDSTONE FACIES:</i> Consists of laminated carbonaceous mudstone containing 20-40% calcite, 40-55% quartz and 10-20% muscovite. Sulphides occur in laminae. In the XY area it is usually the lowest facies in the section to contain laminated sulphides. - <i>CALCAREOUS MUDSTONE FACIES:</i> Consists of grey to greyish black monotonous, calcareous siliceous carbonaceous mudstone. There are no feathery calcite beds or pyrite-calcite blebs in the facies, making it easily distinguishable from the CCMS. - <i>GRADED LIMESTONE FACIES:</i> Is a laminated argillaceous limestone with intercalated carbonaceous limestone laminae. The main rock type in the facies is laminated limestone with laminae up to 0.1-7mm thick. - <i>LIGHT GREY BASAL LIMESTONE FACIES - LGLS:</i> Consists of laminated argillaceous limestone. In the Anniv area it marks the end of the ACTM. It's not always									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-196

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		present in the stratigraphy. - BASAL FACIES: This is a highly contorted and locally foliated carbonaceous mudstone. Unlike the other facies it is not repeated higher in the member. It appears locally to contain the slip zone of a major slump. The facies has only been observed in the YX area. It is 0.1-2m thick. The facies consists of massive carbonaceous siliceous mudstone with lenses and laminae of contorted, slightly carbonaceous chert. Most of the unit is faulted out, with only the bottom portion comprising largely barren unlaminated mudstone and limestone remaining. « 522.70- 524.20 light grey laminated limestone concretion »« 522.70- 524.20 0.2% Zn, Pb: nil » « 524.20- 526.20 Dark grey siliceous mudstone with minor limestone; laminated locally; contains calcareous mudstone-style veining »« 524.20- 526.20 0.3% Zn, Pb: nil » « 526.20- 527.30 dark grey siliceous mudstone with minor limestone; laminated locally; no visible mineralization; no mineralization indicated by NITON » « 527.30- 528.40 Light grey limestone with minor interbedded calcareous mudstone; interpreted as the light grey basal limestone facies; no mineralization. »									
528.40	579.70	CCMS									
		CCMS – Calcareous Mudstone Massive, calcareous, carbonaceous, dark grey mudstone. Most of the member is massive, but rare poorly defined bedding and pyrite-calcite micro-concretions are present. Most diagnostic structures are feathery calcite beds (=thin calcite-cemented concretions, many of them contain pyrite cores) and calcite									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-196

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		<i>pseudo-beds (= fibrous calcite vein parallel to bedding).</i> « lm ca 5.00-10.00mm », « nodules py -3.00% 2.00-20.00mm », « 528.40- 531.40 heavily fractured »« 5% breccia » « @ 532.30 1 cm bed rich in calcite and pyrite crystals so tca 36° » « @ 540.90 pyrite/calcite-rich bed s0 tca 40° » « 548.40- 560.20 heavily fractured; likely includes several minor faults » « @ 561.40 pyrite-rich bed s0 tca 47° » « @ 572.40 compositional lamination defined by calcite crystals with parallel orientation s0 tca 35° »									
579.70	579.70	EOH									

Selwyn Project

Diamond Drill Log

Comprehensive Report for Hole:

XYC-195

Hole No.: XYC-195	Depth: 362.70 m	Horizontal Length: 0.00 m	Project: 1710
Location Data:			
Property:	Selwyn Project	Claim Name:	X 2
Mining District:	Selwyn Basin	Grant Number:	Y 64527
Province/Territory:	Yukon		
UTM Co-Ordinates & Altitude of Drill Hole Collar:			
UTM Easting:	488433.78 m	True Azimuth:	210.0 °
UTM Northing:	6926687.80 m	Hole Angle:	-87.0 °
Elevation (m):	1585.27 m	NTS Name:	Placer Creek
		NTS Number:	105I06
Grid Co-Ordinates of Drill Hole Collar:			
Grid Easting (m):	0.00 m	Grid Name:	HP 06
Grid Northing (m):	0.00 m	Grid Type:	100m
Grid Azimuth:	270.0 °		
Dimond Drilling Contract:			
Drilled By:	NL-01	Date Drilling Start:	07/26/2010
		Date Finish:	08/03/2010
Diamond Drill Core:			
Logged By:	Jelle De Bruyckere	Date Logging Start:	07/31/2010
		Date Finish:	08/03/2010
Legend for Core Logging Codes: PAX			
Core Size:	NQ3	Cemented:	Yes
Casing Depth:	8.90 m	Casing Pulled:	Yes
Water Depth:	0.00 m	Overburden Depth:	8.90 m
Level:			
Section:		Drift:	

Selwyn Project

Diamond Drill Log

Survey Data for Hole

XYC-195

Hole Comments:

Tue, Jul 27 --- Commenced drilling yesterday during day shift. 55 meters drilled over the past two shifts. Currently in likely BSSM, although bioturbations are present sporadically throughout. The core has been generally fairly competent, and drilling is going well with no mechanical issues to report. Darcy now has the Devicore tool in working order.

Wed, Jul 28 --- Drilling going quite well at 113 meters, with 58 meters over the past two shifts. NS had some problems with water loss all night; DS is expected to pull back and grease the rods. Core was not brought back this morning, as NS thought they were pulling a 24 hour shift. Core observed last night was FLMD, with BSSM-FLMD contact at approximately 54 meters.

Thu, Jul 29 --- Drilling going well through competent FLMD at 168 meters. No mechanical problems to report. Note the change to the BSSM-FLMD contact, as earlier light-grey bioturbated mudstone deemed to be part of BSSM. May revise further during detailed log.

Fri, Jul 30 --- Drilling through competent FLMD at 208 meters. Night shift had a problem locking the tube and had to pull rods, but the problem has been addressed.

Sat, Jul 31 --- In USMS at a total depth of 266.4m. Nice competent core.

Sun, Aug 01 --- At morning shift change the total depth was 297m. ACTM was encountered at approximately 282.4m. ACTM intersection is pretty broken up, with 10-15% flt gg.

Mon, Aug 02 --- At morning shift change the total depth was 323m. About 26m was drilled in the past 24hrs. The last 12m of core is barren ACTM, with at the end possibly the basal limestone. We decided to keep on drilling until we are confident enough we hit footwall rocks. The core is still broken up, with sections of flt gg in between. Shut down of the hole is expected to happen at or before target depth.

Tue, Aug 03 --- At yesterday's morning shift change we did indeed see the light grey basal limestone. During the past 24hrs they drilled 40m into footwall rock (CCMS) to a total depth of 362.7. The drill got shut down and will get cemented from 825' to bottom of hole. After that the drill will move to setup #31.

<i>Depth</i>	<i>Dip</i>	<i>Azimuth</i>
0.00	-87.0	210.0
21.60	-86.5	208.5
49.10	-86.1	205.8
73.50	-85.8	214.2
97.80	-85.8	213.6
121.90	-85.8	209.4
146.60	-85.8	212.0
171.00	-85.5	205.6
195.40	-85.6	214.2
219.80	-85.3	211.1

Selwyn Project

Diamond Drill Log

Survey Data for Hole

XYC-195

Selwyn Chihong Mining Ltd.#700-509 Richards Street
Vancouver, British Columbia
Canada V6B 2Z6

244.10	-85.0	205.3
268.50	-84.8	207.7
292.90	-84.3	205.3
317.30	-83.9	204.0
341.70	-83.9	205.9
362.70	-83.7	200.9

Selwyn Project Diamond Drill Log

Hole Number:
XYC-195

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
0.00	8.90	OVBR									
8.90	119.40	BSSM									
BSSM – Backside Siliceous Mudstone Greyish black siliceous mudstone. Randomly-oriented to bedding-parallel bioturbation is common in the bottom of the unit. « 8.90- 199.40 Typical BSSM with bioturbated sections, ranging from 6cm to 11m. Siliceous grey mudstone; few carbonate concretions of which some show bedding. Pyrite occurs as concretions, bands and blebs. Only minor chert was observed. » ◁ @ 19.30 S0 defined by faint btrb S0 tca 47° ▷ ◁ @ 31.50 S0 defined by faint lm in slightly calcareous mudstone S0 tca 21° ▷ ◁ @ 37.70 S0 defined by faint lm in slightly calcareous mudstone S0 tca 25° ▷ ◁ @ 56.60 S0 defined by btrb S0 tca 32° ▷ ◁ @ 69.60 S0 defined by laminated calcareous mdst S0 tca 60° ▷ ◁ @ 85.00 S0 defined by faint lm in siliceous mdst S0 tca 53° ▷											
119.40	226.30	FLMD									
FLMD – Flaggy Mudstone Formation Dark grey mudstone in the upper portions of the unit grading into light grey mudstone to siltstone. Contains abundant wispy bioturbation which ranges from randomly-oriented at the top of the unit to bedding-parallel throughout the majority of the unit. Darker upper section has a strong fetid odour along broken surfaces. « btrb 0.10-2.00cm », « cg xtl crns ca 1.00-5.00% 5.00-150.00cm », « crns py 1.00-5.00% 0.10-0.50mm » « 119.4- 226.3 Typical FLMD » ◁ @ 123.20 S0 defined by btrb S0 tca 38° ▷											

Selwyn Project Diamond Drill Log

Hole Number:
XYC-195

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		< @ 151.90 S0 defined by btrb S0 tca 45° > < @ 151.90 Beta 180° > < @ 161.80 S0 defined by btrb S0 tca 40° > < @ 161.80 Beta 347° > < @ 168.00 S0 defined by faint beds in slightly calcareous mdst S0 tca 35° > < @ 175.00 S0 defined by lm in calcareous mdst S0 tca 57° > < @ 190.30 S0 defined by btrb S0 tca 44° > < @ 190.30 Beta 180° > < @ 217.40 S0 defined by btrb S0 tca 44° > < @ 217.40 Beta 150° > « 218.30- 225.90 Darker (due to higher carbonaceous content) siliceous mudstone with significant calcareous sections » < @ 225.50 S0 defined by faint beds S0 tca 56° > « 225.90- 226.30 Minor flt »« flt gg 15%»« bx 25%»« brco 15%»									
226.30	282.00	USMS	631701	243.50	244.00	0.50	0.25	0.10	1.00	5.00	2.50
		USMS – Upper Siliceous Mudstone	631702	244.00	244.40	0.40	1.49	6.51	7.00	240.00	0.23
			631703	244.40	244.60	0.20	0.12	0.01	1.00	5.00	24.00
		Consists of interlaminated dark grey to black mudstone and light to medium grey chert. Regionally, a 1m thick graptolite zone occurs 15m below the top of the upper unit, this is usable as a horizon. The USMS is divided into 3 units. The Lower Unit contains abundant limestone concretions and Galena and sphalerite micro-concretions occur locally near the base of this unit. « gra , lm chrt -20.00% », « cg xtl sph crns ca 5.00-20.00cm », « bed chrt 10.00-15.00% »	631704	276.80	277.00	0.20	0.03	0.23	1.00	5.00	0.13
			631705	281.50	282.00	0.50	0.05	0.09	1.00	5.00	0.56
		« 226.30- 282.00 Typical USMS »									
		< @ 229.20 S0 defined by chert bands S0 tca 49° > < @ 229.20 Beta 150° >									
		< @ 236.60 S0 defined by chert bands S0 tca 39° >									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-195

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
◁ @ 239.70 S0 defined by parallel py beds S0 tca 50° ▷ @ 239.70 Beta 160° ▷ « 244.00- 244.40 Mineralized section. 5.7% Zn and 2.4% Pb. Well developed lm. Galena blebs and stringers visible. » ◁ @ 244.30 S0 defined by well developed lamination S0 tca 43° ▷ @ 244.30 Beta 90° ▷ ◁ @ 258.30 S0 defined by thick chert bands S0 tca 39° ▷ ◁ @ 266.80 S0 defined by faint beds, parallel elongated/lenticular pyrite concretions S0 tca 55° ▷ « 268.60- 282.00 This section of USMS shows the typical vugs in the core, which is often an indicator that ACTM is closeby. Core still looks like USMS, but does contain minor Zn (<1%) and even less Pb . »											
282.00	321.10	ACTM	631706	282.00	282.40	0.40	0.03	0.01	1.00	5.00	6.00
ACTM – Active Member			631707	282.40	283.60	1.20	4.05	10.92	4.00	390.00	0.37
			631708	283.60	284.90	1.30	5.31	5.75	2.00	200.00	0.92
			631709	284.90	285.10	0.20	0.10	0.31	1.00	5.00	0.32
			631710	285.10	286.50	1.40	1.15	6.99	3.00	180.00	0.16
			631711	285.10	286.50	1.40	1.28	5.28	1.00	140.00	0.24
			631712	286.50	287.40	0.90	0.65	3.43	1.00	90.00	0.19
			631713	287.40	287.50	0.10	0.03	0.06	1.00	5.00	0.50
			631714	287.50	288.20	0.70	0.04	1.16	1.00	30.00	0.03
			631715	288.20	289.40	1.20	1.88	8.89	3.00	240.00	0.21
			631716	289.40	289.80	0.40	2.99	16.39	5.00	450.00	0.18
			631717	289.80	291.30	1.50	0.05	0.08	1.00	5.00	0.63
			631718	291.30	291.50	0.20	4.28	2.95	1.00	80.00	1.45
			631719	291.50	292.20	0.70	1.49	4.02	1.00	110.00	0.37
			631720	292.20	292.20	0.00	0.01	0.01	1.00	5.00	2.00
			631721	292.20	292.50	0.30	0.43	1.48	1.00	50.00	0.29

Selwyn Project Diamond Drill Log

Hole Number:
XYC-195

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
- WHITISH GREY ZN-PB MUDSTONE FACIES: Is a laminated cherty rock containing up to 70% sulphides. Mineralization: quartz, sphalerite and galena are the major minerals with only minor amounts of pyrite and locally calcite. Sedimentary diagenetic structures are common and well displayed in the facies, such as: lamination, pseudo-beds, calcite nodules & limestone nodules and abundant water escape structures. Most obvious structure in facies is cross-cutting veins containing massive sphalerite and galena with minor pyrite. They range in width from 0.5 to 10mm. - THIN BEDDED CHERTY MUDSTONE FACIES: Consists of rhythmic intercalated laminae of chert, carbonaceous mudstone and minor micrite. This facies contains significant amounts of Zn and Pb sulphides. - CHERTY MUDSTONE FACIES: Consists of a greyish black monotonous siliceous, carbonaceous mudstone. It is most typically found overlying the thin bedded calcareous mudstone facies. - THIN BEDDED CALCAREOUS MUDSTONE FACIES: Consists of laminated carbonaceous mudstone containing 20-40% calcite, 40-55% quartz and 10-20% muscovite. Sulphides occur in laminae. In the XY area it is usually the lowest facies in the section to contain laminated sulphides. - CALCAREOUS MUDSTONE FACIES: Consists of grey to greyish black monotonous, calcareous siliceous carbonaceous mudstone. There are no feathery calcite beds or pyrite-calcite blebs in the facies, making it easily distinguishable from the CCMS. - GRADED LIMESTONE FACIES: Is a laminated argillaceous limestone with intercalated carbonaceous limestone laminae. The main rock type in the facies is laminated limestone with laminae up to 0.1-7mm thick. - LIGHT GREY BASAL LIMESTONE FACIES - LGLS: Consists of laminated argillaceous			631722	292.50	293.00	0.50	1.39	7.70	1.00	210.00	0.18
			631723	293.00	293.60	0.60	0.83	1.46	1.00	40.00	0.57
			631724	293.60	294.20	0.60	6.99	31.34	8.00	720.00	0.22
			631725	294.20	294.60	0.40	5.23	27.56	5.00	620.00	0.19
			631726	294.60	295.00	0.40	2.52	19.07	1.00	490.00	0.13
			631727	295.00	295.80	0.80	3.38	8.82	2.00	250.00	0.38
			631728	295.80	296.20	0.40	0.57	1.88	1.00	50.00	0.30
			631729	296.20	297.80	1.60	2.52	6.14	3.00	160.00	0.41
			631730	297.80	297.80	0.00	5.91	7.03	70.00	190.00	0.84
			631731	297.80	299.30	1.50	1.22	2.25	4.00	60.00	0.54
			631732	299.30	300.20	0.90	2.35	7.23	3.00	220.00	0.33
			631733	300.20	300.70	0.50	12.39	21.75	6.00	810.00	0.57
			631734	300.70	301.10	0.40	4.19	19.01	5.00	440.00	0.22
			631735	301.10	301.70	0.60	5.82	37.81	8.00	950.00	0.15
			631736	301.70	302.50	0.80	1.40	12.61	2.00	340.00	0.11
			631737	302.50	303.00	0.50	3.36	7.61	1.00	230.00	0.44
			631738	303.00	303.30	0.30	0.29	0.04	1.00	5.00	7.25
			631739	303.30	304.80	1.50	0.01	0.01	1.00	5.00	2.00
			631740	304.80	305.60	0.80	0.05	0.29	1.00	10.00	0.17
			631741	304.80	305.60	0.80	0.04	0.12	1.00	5.00	0.33
			631742	305.60	306.50	0.90	0.01	0.01	1.00	5.00	2.00
			631743	306.50	307.40	0.90	0.01	0.01	1.00	5.00	2.00
			631744	307.40	307.70	0.30	0.01	0.01	1.00	5.00	2.00
			631745	307.70	308.50	0.80	0.35	0.07	1.00	5.00	5.00
			631746	308.50	309.70	1.20	0.95	0.63	3.00	20.00	1.51
			631747	309.70	311.20	1.50	0.43	0.61	3.00	20.00	0.70
			631748	311.20	312.40	1.20	0.12	0.63	1.00	20.00	0.19
			631749	312.40	313.50	1.10	0.20	1.99	3.00	70.00	0.10
			631750	313.50	313.50	0.00	0.01	0.01	1.00	5.00	2.00
			631751	313.50	314.80	1.30	0.06	0.38	1.00	10.00	0.16
			631752	314.80	315.80	1.00	0.01	0.01	1.00	5.00	2.00
			631753	315.80	317.00	1.20	0.01	0.03	1.00	5.00	0.33

Selwyn Project Diamond Drill Log

Hole Number:
XYC-195

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		limestone. In the Anniv area it marks the end of the ACTM. It's not always present in the stratigraphy.	631754	317.00	318.70	1.70	0.10	0.38	1.00	10.00	0.26
			631755	318.70	320.30	1.60	0.19	1.07	1.00	40.00	0.18
			631756	320.30	321.10	0.80	0.01	0.01	1.00	5.00	2.00
		- BASAL FACIES: This is a highly contorted and locally foliated carbonaceous mudstone. Unlike the other facies it is not repeated higher in the member. It appears locally to contain the slip zone of a major slump. The facies has only been observed in the YX area. It is 0.1-2m thick. The facies consists of massive carbonaceous siliceous mudstone with lenses and laminae of contorted, slightly carbonaceous chert. « 282.00- 282.40 Siliceous carbonaceous mudstone with <0.3% Pb. Broken up core and 15% flt gg. » « 282.40- 284.90 Siliceous mudstone with Sph + Ga. 11% Zn & 6% Pb. Visible Sph bands and Ga blebs + stringers. This section contains a 10cm piece of high grade (>30% combined). Lamination is moderately developed. No total recovery. About 10% flt gg. Fair amount of pyrite. » « 284.90- 285.10 Carbonate » « 285.10- 286.50 Mainly siliceous brco. Average mineralization. 7% Zn & 3% Pb. Poor recovery. 20% flt gg » « 286.50- 287.40 Siliceous carbonaceous mdst. 2% Zn & 0.4% Pb. Very poor recovery. » « 287.40- 287.50 Bedded carbonate » « 287.50- 288.20 Siliceous carbonaceous mdst. 1% Zn & 0.2% Pb. Poor recovery. » « 288.20- 289.40 Siliceous to slightly calcareous mdst with minor carbonate crns. Fair amount of pyrite. Locally developed lm. 2% Zn & 7% Pb. »									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-195

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		« 289.40- 289.80 Calcareous mdst with strong mineralization. 20% Zn & 12% Pb »									
		« 289.80- 291.30 Limestone »									
		« 291.30- 291.50 Limestone with up to 2% Pb »									
		« 291.50- 292.20 Siliceous carbonaceous mudstone. Weak mineralization: 3% Zn & 1% Pb. Broken up core with 10% flt gg »									
		« 292.20- 292.50 Limestone »									
		« 292.50- 293.00 Calcareous carbonaceous mudstone, weakly mineralized: 3% Zn & 3% Pb »									
		« 293.00- 293.60 Carbonaceous slightly calcareous mudstone. Almost barren. 0.6% Zn & 0.3% Pb »									
		« 293.60- 294.60 High grade ore: 24% Zn & 14% Pb. Broken up core. Lots of vugs. <5% flt gg. Dark coloured. »									
		« 294.60- 295.00 High grade ore (Whitish Grey Zn/Pb Mudstone Facies): 17% Zn & 9% Pb. Competent core, as opposed to the previous section. »									
		« 295.00- 295.80 Mainly siliceous carbonaceous mudstone. Visible Ga stringers. Broken up core. About 5% flt gg. Average mineralization: 7% Zn & 3% Pb »									
		« 295.80- 296.20 Very calcareous barren mudstone. »									
		« 296.20- 297.80 Calcareous carbonaceous broken up mudstone. No total recovery. About 10% flt gg. Average mineralization: 2% Zn & 4% Pb »									
		« 297.80- 300.20 Calcareous carbonaceous broken up mudstone with minor carbonate concretions in between. Less than 5% flt gg. Weak mineralization: 3%									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-195

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		Zn & 1% Pb. Visible Ga stringers. » « 300.20- 302.50 High grade ore. Whitish Grey Zn/Pb Mudstone Facies. Strongly mineralized: 20% Zn & 10% Pb » « 302.50- 303.00 Calcareous mudstone with locally moderately developed lamination. Average mineralization: 6% Zn & 4% Pb. » « 303.00- 303.30 Calcareous barren mudstone » « 303.30- 304.80 Limestone » « 304.80- 306.50 Siliceous barren mudstone with some minor limestone. » « 306.50- 307.40 Calcareous barren mudstone » « 307.40- 307.70 Siliceous barren mudstone » « 307.70- 308.50 Calcareous thinly bedded mudstone. Barren except for 2 Ga stringers. » « @ 308.20 S0 defined by parallel thin beds S0 tca 40° » « @ 308.20 Beta 0° » « 308.50- 309.70 Siliceous mudstone with very weak mineralization: 0.3% Zn & 0.3% Pb » « 309.70- 313.50 Calcareous mudstone with very weak mineralization: 0.2% Zn & 0.2% Pb » « 313.50- 314.80 Siliceous mudstone. Almost barren: <0.5% Zn » « 314.80- 315.80 Mainly limestone » « 315.80- 317.00 Slightly calcareous barren mudstone »									

Selwyn Project

Diamond Drill Log

Hole Number:
XYC-195
Selwyn Chihong Mining Ltd.
 #700-509 Richards Street
 Vancouver, British Columbia
 Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		« 317.00- 320.30 Siliceous mudstone. Badly broken. Poor recovery. »« flt gg 20%»« bx 20%»« brco 50%» « 320.30- 321.10 Basal Limestone »									
321.10	362.70	CCMS ----- CCMS – Calcareous Mudstone Massive, calcareous, carbonaceous, dark grey mudstone. Most of the member is massive, but rare poorly defined bedding and pyrite-calcite micro-concretions are present. Most diagnostic structures are feathery calcite beds (=thin calcite-cemented concretions, many of them contain pyrite cores) and calcite pseudo-beds (= fibrous calcite vein parallel to bedding). « lm ca 5.00-10.00mm », « nodules py -3.00% 2.00-20.00mm » « Classic CCMS » ‹ @ 327.20 S0 defined by faint bed S0 tca 45° › ‹ @ 333.40 S0 defined by faint bed S0 tca 49° › ‹ @ 337.60 S0 defined by faint bed S0 tca 47° › ‹ @ 341.30 S0 defined by faint bed S0 tca 42° ›× @ 341.30 Beta 132° › ‹ @ 341.90 S0 defined by faint bed S0 tca 49° ›× @ 341.90 Beta 137° › ‹ @ 343.90 S0 defined by faint bed S0 tca 40° ›× @ 343.90 Beta 140° › ‹ @ 345.70 S0 defined by faint bed S0 tca 40° › ‹ @ 353.20 S0 defined by faint bed S0 tca 48° › ‹ @ 356.80 S0 defined by faint bed S0 tca 49° ›									
362.70	362.70	EOH									

Diamond Drill Log

Comprehensive Report for Hole:

XYC-194

Hole No.: XYC-194	Depth: 309.70 m	Horizontal Length: 0.00 m	Project: 1710
Location Data:			
Property:	Selwyn Project	Claim Name:	X 13
Mining District:	Selwyn Basin	Grant Number:	Y64538
Province/Territory:	Yukon		
UTM Co-Ordinates & Altitude of Drill Hole Collar:			
UTM Easting:	488696.84 m	True Azimuth:	210.0 °
UTM Northing:	6926530.20 m	Hole Angle:	-83.0 °
Elevation (m):	1632.09 m	NTS Name:	Placer Creek
		NTS Number:	105I06
Grid Co-Ordinates of Drill Hole Collar:			
Grid Easting (m):	0.00 m	Grid Name:	HP 06
Grid Northing (m):	0.00 m	Grid Type:	100m
Grid Azimuth:	270.0 °		
Dimond Drilling Contract:			
Drilled By:	NL-02	Date Drilling Start:	07/22/2010
		Date Finish:	07/29/2010
Diamond Drill Core:			
Logged By:	Matthew Jodrey	Date Logging Start:	07/24/2010
		Date Finish:	08/02/2010
Legend for Core Logging Codes: PAX			
Core Size:	NQ3	Cemented:	Yes
Casing Depth:	16.80 m	Casing Pulled:	Yes
Water Depth:	0.00 m	Overburden Depth:	16.80 m
Level:	Section:	Drift:	

Selwyn Project

Diamond Drill Log

Survey Data for Hole

XYC-194

Hole Comments:

Thu, Jul 22 --- Day shift and night shift arrived yesterday and began to set up the drill, which was already positioned on location. Some casing was put down yesterday, but drilling will begin today, as there was no night shift last night.

=====

Fri, Jul 23 --- Much of day shift yesterday was spent configuring the split tube set-up to be compatible with the devicore extension, and only a small amount of casing was put down. Night shift commenced drilling after approximately 25 feet of casing was put down, thinking they were close to bedrock, but they were still in overburden after approximately 50 feet. The rods were then pulled, and casing was put down to 55 feet by end of night shift.

=====

Sat, Jul 24 --- Drilling going fairly well now, at 54.70 meters, in FLMD with the BSSM-FLMD contact at 46.9 meters. The core is quite competent, and there are no mechanical problems to report with the drill. Darcy has addressed the Devicore problem with this drill. Day shift forgot to do a Flexit test.

=====

Sun, Jul 25 --- Very slow drilling despite generally quite competent rock. 38 meters of core drilled over the past 24 hours, but only 13 metres drilled by night shift, which is having problems getting used to the drill and/or the rock. Currently in a dark grey portion of FLMD, with minor bioturbations still present locally. A packer test was conducted yesterday during day shift, which took approximately 4 hours.. Night shift pulled rods due to significant vibration in the hole.

=====

Mon, Jul 26 --- Still slow drilling in FLMD at 137.7 meters. The core has been very blocky and fractured over the past several meters, but overall has been quite competent throughout.

=====

Tue, Jul 27 --- Drilling in competent FLMD, at 182.7 meters with 45 meters drilled over the past day. NS had a good shift last night, and they seem to be familiarizing themselves with the rock/drill.

=====

Wed, Jul 28 --- Drilling going well in generally competent USMS at 252.3 meters; 70 meters drilled in the past day. The FLMD-USMS contact is at approximately 190 meters. No mechanical issues to report.

=====

Thu, Jul 29 --- Hit Active Member during day shift yesterday at 256.3 meters. Moderate mineralization is visible from 256.3 meters to approximately 260 meters, followed very broken-up/faulted limestone and mudstone with little visible mineralization. Current depth is 275 meters, with 23 meters of tough drilling over the past day.

=====

Fri, Jul 30 --- Shut down XYC-194 after day shift in CCMS at 309.7 meters. Moved NL-03 last night to XYC-196 (setup # 29) NS started putting down casing last night and drilling will begin this morning.

Selwyn Project

Diamond Drill Log

Survey Data for Hole

XYC-194

<i>Depth</i>	<i>Dip</i>	<i>Azimuth</i>
0.00	-83.0	210.0
40.00	-82.5	210.2
65.70	-81.9	206.0
114.70	-81.5	210.1
129.70	-81.6	207.1
157.70	-81.8	202.5
175.00	-80.7	207.0
202.00	-80.7	202.0
225.70	-80.7	202.3
249.60	-80.5	203.9
276.70	-79.7	204.6
301.00	-80.3	210.2

Selwyn Project Diamond Drill Log

Hole Number:
XYC-194

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
0.00	16.80	OVBR									
16.80	102.90	BSSM									
<i>BSSM – Backside Siliceous Mudstone</i> <i>Devonian Siliceous Mudstone – Upper Chert Formation</i> <i>Greyish black siliceous mudstone;laminated locally. Limestone concretions/beds observed throughout. Randomly-oriented to bedding-parallel bioturbation is common in the bottom of the unit. Minor chert banding observed throughout « lm chrt 75.00-95.00% », « btrb 0.10-2.00cm »</i> <i>< @ 26.80 S0 tca 70° ></i> <i>< @ 41.60 S0 tca 43° ></i> <i>< @ 42.70 S0 tca 53° > < @ 42.70 Beta 150° ></i> <i>« 46.00- 50.30 wk brtb »</i> <i>< @ 49.80 S0 tca 45° ></i> <i>« 50.30- 62.40 str brtb »</i> <i>< @ 50.40 S0 tca 39° < @ 50.40 Beta 180° ></i> <i>< @ 56.90 S0 tca 36° ></i> <i>« 62.40- 66.70 lm lmst »</i> <i>« 66.70- 67.30 str gg flt »</i> <i>« 67.30- 102.90 str cur chrt banding »</i> <i>< @ 69.60 S0 tca 34° ></i>											

Selwyn Project Diamond Drill Log

Hole Number:
XYC-194

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
< @ 79.20	S0 tca 33° >										
< @ 83.40	S0 tca 31° <										
« 98.50- 102.90	wk brtb »										
< @ 98.80	S0 tca 28° >										
< @ 99.60	S0 tca 32° > < @ 99.60	Beta 155° >									
102.90	190.30	FLMD									
FLMD – Flaggy Mudstone Formation											
Dark grey mudstone in the upper portions of the unit grading into light grey mudstone to siltstone. Contains abundant wispy bioturbation which ranges from randomly-oriented at the top of the unit to bedding-parallel throughout the majority of the unit. Darker upper section has a strong fetid odour along broken surfaces. Contains limestone concretions locally; « btrb 0.10-2.00cm », « cg xtl crns ca 1.00-5.00% 5.00-150.00cm », « crns py 1.00-5.00% 0.10-0.50mm »,											
< @ 123.10	S0 tca 32° >										
< @ 138.60	S0 tca 34° >										
< @ 152.90	S0 tca 33° >										
< @ 161.70	S0 tca 47° >										
< @ 162.80	S0 tca 41° > < @ 162.80	Beta 200° >									
« 165.70- 171.90	grap flt »										
« 174.20- 190.30	med gra wk btrb »										

Selwyn Project Diamond Drill Log

Hole Number:
XYC-194

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
< @ 187.10 S0 tca 34° >											
190.30	256.20	USMS	631401	219.80	220.20	0.40	0.09	0.15	1.00	5.00	0.60
USMS – Upper Siliceous Mudstone			631402	220.20	220.60	0.40	0.17	3.04	4.00	90.00	0.06
Consists of interlaminated dark grey to black mudstone and light to medium grey chert. Regionally, a 1m thick graptolite zone occurs 15m below the top of the upper unit, this is usable as a horizon. The USMS is divided into 3 units. The Lower Unit contains abundant limestone concretions and Galena and sphalerite micro-concretions occur locally near the base of this unit. « gra , lm chrt -20.00% », « cg xtl sph crns ca 5.00-20.00cm », « bed chrt 10.00-15.00% »,			631403	220.60	220.90	0.30	0.21	1.81	3.00	50.00	0.12
			631404	220.90	221.20	0.30	0.31	4.92	5.00	150.00	0.06
			631405	221.20	221.60	0.40	0.01	0.01	1.00	5.00	2.00
< @ 204.40 S0 tca 44° >											
< @ 215.50 S0 tca 32° >											
« 220.20- 220.40 Range of Active Member; light grey, laminated, strongly calcareous, visible mineralization; NITON grades: 5.0 % Zn, 0.7 % Pb »											
« 220.60- 220.80 Active Member range; light grey, laminated, visible mineralization; NITON: 6.2 % Zn, 0.6% Pb »											
« 220.90- 221.10 Active Member range; dark grey, laminated mudstone with weak visible mineralization; NITON: 5.6% Zn, 0.9 % Pb »											
< @ 224.90 S0 tca 38° >											
« 234.90- 236.40 finely laminated, dark grey, weakly calcareous mudstone; approaching Active Member in appearance, but unmineralized. »											
< @ 237.10 S0 tca 37° >											
< @ 240.60 S0 tca 48° > < @ 240.60 Beta 118° >											
< @ 247.20 S0 tca 57° >											

Selwyn Project Diamond Drill Log

Hole Number:
XYC-194

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
256.20	270.10	ACTM									
ACTM – Active Member			631406	256.20	256.70	0.50	2.16	6.49	3.00	340.00	0.33
The ACTM consists of a repetitive, possibly rhythmic, sequence of intercalated carbonaceous mudstone, cherty mudstone, chert and limestone and locally contains economically significant Zn and Pb sulphides (see bold marked facies), mainly in its sections with well developed lamination. Because of its heterogeneity, the member is distinctive and easily identified. ===== The ACTM has 8 different facies: ===== - GREY CHERT FACIES: Consists of laminated medium light grey to medium dark grey chert. Mineralization: 95-99% quartz and up to 5% secondary calcite. - WHITISH GREY ZN-PB MUDSTONE FACIES: Is a laminated cherty rock containing up to 70% sulphides. Mineralization: quartz, sphalerite and galena are the major minerals with only minor amounts of pyrite and locally calcite. Sedimentary diagenetic structures are common and well displayed in the facies, such as: lamination, pseudo-beds, calcite nodules & limestone nodules and abundant water escape structures. Most obvious structure in facies is cross-cutting veins containing massive sphalerite and galena with minor pyrite. They range in width from 0.5 to 10mm. - THIN BEDDED CHERTY MUDSTONE FACIES: Consists of rhythmic intercalated laminae of chert, carbonaceous mudstone and minor micrite. This facies contains significant amounts of Zn and Pb sulphides. - CHERTY MUDSTONE FACIES: Consists of a greyish black monotonous siliceous, carbonaceous mudstone. It is most typically found overlying the thin bedded calcareous mudstone facies. - THIN BEDDED CALCAREOUS MUDSTONE FACIES: Consists of laminated			631407	256.70	257.00	0.30	1.02	5.70	1.00	230.00	0.18
			631408	257.00	257.50	0.50	1.77	9.83	2.00	390.00	0.18
			631409	257.50	257.90	0.40	1.95	7.92	1.00	300.00	0.25
			631410	257.90	258.30	0.40	1.78	8.77	3.00	310.00	0.20
			631411	257.90	258.30	0.40	1.52	8.17	3.00	290.00	0.19
			631412	258.30	258.90	0.60	0.16	0.07	1.00	5.00	2.29
			631413	258.90	259.30	0.40	0.13	1.56	1.00	40.00	0.08
			631414	259.30	259.90	0.60	1.48	10.17	3.00	270.00	0.15
			631415	259.90	260.20	0.30	0.64	0.16	1.00	5.00	4.00
			631416	260.20	260.50	0.30	0.37	1.68	1.00	40.00	0.22
			631417	260.50	261.40	0.90	0.50	2.66	1.00	80.00	0.19
			631418	261.40	261.70	0.30	0.27	0.67	1.00	20.00	0.40
			631419	261.70	263.10	1.40	0.05	0.43	1.00	10.00	0.12
			631420	263.10	263.10	0.00	0.01	0.01	1.00	5.00	2.00
			631421	263.10	263.40	0.30	1.68	5.14	1.00	120.00	0.33
			631422	263.40	263.90	0.50	4.71	16.65	5.00	420.00	0.28
			631423	263.90	265.00	1.10	1.31	3.69	1.00	100.00	0.36
			631424	265.00	265.30	0.30	1.07	8.12	1.00	230.00	0.13
			631425	265.30	266.80	1.50	1.78	1.67	1.00	70.00	1.07
			631426	266.80	267.90	1.10	0.11	0.13	1.00	5.00	0.85
			631427	267.90	268.20	0.30	0.01	0.01	1.00	5.00	2.00
			631428	268.20	268.80	0.60	0.34	0.01	1.00	5.00	34.00
			631429	268.80	270.10	1.30	0.01	0.01	1.00	5.00	2.00

Selwyn Project Diamond Drill Log

Hole Number:
XYC-194

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		carbonaceous mudstone containing 20-40% calcite, 40-55% quartz and 10-20% muscovite. Sulphides occur in laminae. In the XY area it is usually the lowest facies in the section to contain laminated sulphides. - CALCAREOUS MUDSTONE FACIES: Consists of grey to greyish black monotonous, calcareous siliceous carbonaceous mudstone. There are no feathery calcite beds or pyrite-calcite blebs in the facies, making it easily distinguishable from the CCMS. - GRADED LIMESTONE FACIES: Is a laminated argillaceous limestone with intercalated carbonaceous limestone laminae. The main rock type in the facies is laminated limestone with laminae up to 0.1-7mm thick. - LIGHT GREY BASAL LIMESTONE FACIES - LGLS: Consists of laminated argillaceous limestone. In the Anniv area it marks the end of the ACTM. It's not always present in the stratigraphy. - BASAL FACIES: This is a highly contorted and locally foliated carbonaceous mudstone. Unlike the other facies it is not repeated higher in the member. It appears locally to contain the slip zone of a major slump. The facies has only been observed in the YX area. It is 0.1-2m thick. The facies consists of massive carbonaceous siliceous mudstone with lenses and laminae of contorted, slightly carbonaceous chert. « 256.20- 257.50 Laminated siliceous mudstone with minor limestone. Moderate visible mineralization; NITON: 6.2% Zn, 3.5% Pb. » « 257.50- 257.90 Light grey limestone with visible sphalerite nodules; NITON: 4.4% Zn, 1.7% Pb. » « 257.90- 259.90 finely laminated siliceous mudstone; moderate visible mineralization; NITON: 3.1% Zn. 0.9% Pb »									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-194

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
« 259.90- 260.20 Light grey limestone; no visible mineralization; NITON: 0.2% Zn, 0% Pb »											
« 260.20- 260.50 weakly laminated calcareous mudstone with little visible mineralization; NITON: 1.1% Zn, 0.4 % Pb »											
« 260.50- 261.70 Medium-dark grey limestone; no visible mineralization; NITON: 0.8% Zn, 0.3% Pb »											
« 261.70- 263.40 Unlaminated, weakly calcareous, mudstone; NITON: 0.5% Zn, 0.1% Pb »											
« 263.40- 265.00 Weakly laminated, broken-up, calcareous mudstone with weak visible mineralization; NITON: 6.0% Zn, 2.6% Pb »											
« 265.00- 265.30 Laminated calcareous mudstone with minor limestone; weak visible mineralization; NITON: 4.6% Zn, 1.5% Pb »											
« 265.30- 267.90 Limestone, fractured, with no visible mineralization; NITON: 0.4% Zn, 0.6% Pb »											
« 267.90- 268.20 Weakly laminated siliceous mudstone with no visible mineralization; NITON: nil »											
« 268.20- 268.80 Very broken-up / brecciated limestone; NITON: Zn: nil; Pb: 0.2% »											
« 268.80- 270.10 Competent limestone; weakly laminated; NITON: Zn: nil, Pb: 0.1% »											
270.10	309.70	CCMS	631430	270.10	270.10	0.00	0.87	1.30	211.00	90.00	0.67
CCMS – Calcareous Mudstone											
Massive, calcareous, carbonaceous, dark grey mudstone. Most of the member is massive, but rare poorly defined bedding and pyrite-calcite micro-concretions											

[illegible]

Diamond Drill Log

Comprehensive Report for Hole:

XYC-193

Hole No.: XYC-193	Depth: 279.50 m	Horizontal Length: 0.00 m	Project: 1710
Location Data:			
Property:	Selwyn Project	Claim Name:	X 13
Mining District:	Selwyn Basin	Grant Number:	Y64538
Province/Territory:	Yukon		
UTM Co-Ordinates & Altitude of Drill Hole Collar:			
UTM Easting:	488863.44 m	True Azimuth:	182.5 °
UTM Northing:	6926424.12 m	Hole Angle:	-84.0 °
Elevation (m):	1651.66 m	NTS Name:	Placer Creek
		NTS Number:	105I06
Grid Co-Ordinates of Drill Hole Collar:			
Grid Easting (m):	0.00 m	Grid Name:	HP 06
Grid Northing (m):	0.00 m	Grid Type:	100m
Grid Azimuth:	242.5 °		
Dimond Drilling Contract:			
Drilled By:	NL-01	Date Drilling Start:	07/18/2010
		Date Finish:	07/25/2010
Diamond Drill Core:			
Logged By:	Matthew Jodrey	Date Logging Start:	07/20/2010
		Date Finish:	08/03/2010
Legend for Core Logging Codes: PAX			
Core Size:	NQ3	Cemented:	Yes
Casing Depth:	6.00 m	Casing Pulled:	Yes
Water Depth:	0.00 m	Overburden Depth:	6.00 m
Level:	Section:	Drift:	

Selwyn Project

Diamond Drill Log

Survey Data for Hole

XYC-193

Hole Comments:

Sun, Jul 18 --- XYC-192 got shut down around 1.30pm yesterday in CCMS at a depth of 450.5m. The hole was taksed at 870' and was cemented all the way up to 500'. The drill was moved to setup #10 in the evening, where XYC-193 is going to be drilled. Last night they put in 20' casing and cored to a depth of 27'. No core has arrived in camp yet.

=====

Mon, Jul 19 --- The hole is at 52m and either in a FLMD appearing section of the BSSM or solid FLMD. To be determined once there there is more core. 44. was drilled in the past 24hrs. The core is rather competent, with locally small amounts of flt gg. There was return loss around 125', the hole is dry right now.

=====

Tue, Jul 20 --- Total depth is 79.6m. In FLMD, mostly bioturbated, some short featureless sections. First packer test was done during yesterday's dayshift. Zero water pressure at the gauge.

=====

Wed, Jul 21 --- Total depth is 99.7m. Still in FLMD. Drilling goes rather slow. They haven't gotten the return in the hole back.

=====

Thu, Jul 22 --- Drilling was much better with more competent core over the past 24 hours. FLMD-USMS contact at approximately 124 meters. USMS is very competent, showing typical cherty banding. No mechanical problems to report.

=====

Fri, Jul 23 --- Drilling going well, total depth 183 meters, with 40 meters over the past day. Still in USMS, showing typical cherty bands and concretions. No mechanical problems to report. Three successful packer tests have now been completed, with pressure increasing in the formation with depth. At least one more packer test will be conducted, one today.

=====

Sat, Jul 24 --- Slow drilling at 220 meters. Still in typical USMS. The core is blocky and fractured, with some small faults. No mechanical problems to report with the drill. The Devicore on this drill is now experiencing data download problems, which Darcy is working hard to address.

=====

Sun, Jul 25 --- At 247 meters now, having drilled 28 meters over the past two shifts. Very slow drilling through mostly broken-up, faulted rock. Between 217 and 237 meters the rock is very faulted and broken up, with abundant fault gouge and some short competent sections. 2 meter section of mainly competent rock at 226-228 exhibits very strong mineralization (Niton readings too high - likely 20-30 % Zn, 15-25% Pb), but is bounded by faults on both sides. Mineralized rock is light grey, but lacks typical light grey texture. Mineralization is absent after 228 meters. From 233-235 meters a significant portion of faulted, gouge-rich core was washed out and lost. From 237 - 247 the rock is largely competent, monotonous dark grey mudstone - possibly CCMS, but will have to drill more.

=====

Mon, Jul 26 --- Shut down hole in definite footwall at 279.5 meters after 42.5 meters of competent CCMS. Last packer test was conducted at approximately 182 meters, and the hole was cemented from 213 meters to bottom. Moving to setup # 27 today, which will become XYC-195.

Selwyn Project

Diamond Drill Log

Survey Data for Hole

XYC-193

<i>Depth</i>	<i>Dip</i>	<i>Azimuth</i>
0.00	-84.0	182.5
24.40	-83.3	183.4
52.10	-82.4	184.1
73.50	-82.0	186.3
97.80	-81.7	186.5
122.20	-81.1	186.5
143.60	-81.0	188.9
171.00	-80.7	187.8
195.40	-80.6	184.4
219.80	-80.2	188.3
243.50	-80.0	188.7
268.50	-79.8	189.8

Selwyn Project Diamond Drill Log

Hole Number:
XYC-193

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
0.00	6.00	OVBR									
6.00	23.40	BSSM									
<i>BSSM – Backside Siliceous Mudstone</i>											
<i>Devonian Siliceous Mudstone – Upper Chert Formation</i>											
<i>Greyish black laminated chert and siliceous mudstone. Randomly-oriented to bedding-parallel bioturbation is common in the bottom of the unit; includes cherty bands, which are atypical for BSSM « lm chrt 75.00-95.00% », « btrb 0.10-2.00cm »,</i>											
<i>« 14.10- 22.20 Very broken up »</i>											
<i>« @ 15.10 s0 tca 63° »</i>											
23.40	124.20	FLMD									
<i>FLMD – Flaggy Mudstone Formation</i>											
<i>Dark grey mudstone in the upper portions of the unit grading into light grey mudstone to siltstone. Contains abundant wispy bioturbation which ranges from randomly-oriented at the top of the unit to bedding-parallel throughout the majority of the unit. Darker upper section has a strong fetid odour along broken surfaces. « btrb 0.10-2.00cm », « cg xtl crns ca 1.00-5.00% 5.00-150.00cm », « crns py 1.00-5.00% 0.10-0.50mm »,</i>											
<i>« 23.40- 31.60 Transitional from BSSM; typical light grey mudstone (60%) interbedded with dark grey mudstone (40%) »</i>											
<i>« @ 26.30 s0 tca 66° »</i>											
<i>« @ 41.90 s0 tca 68° »</i>											
<i>« @ 47.80 s0 tca 72° »</i>											

Selwyn Project Diamond Drill Log

Hole Number:
XYC-193

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
< @ 53.00 s0 tca 68° < @ 53.00 Beta 200° > > < @ 65.10 s0 tca 62° > « 68.80- 82.60 Very broken-up » « 71.00- 75.90 Fine grained, medium grey, locally laminated limestone with gradational contacts (not concretion?) » < @ 73.30 s0 tca 74° > < @ 87.60 s0 tca 66° > « 89.70- 103.20 gouge and breccia-rich flt » « 103.20- 124.20 Weakly to strongly calcareous, despite maintaining typical FLMD appearance » < @ 120.30 s0 tca 20° < @ 120.30 Beta 230° >											
124.20	225.20	USMS	631151	152.70	153.60	0.90	0.11	0.11	1.00	5.00	1.00
USMS – Upper Siliceous Mudstone			631152	153.60	154.00	0.40	1.54	10.80	14.00	290.00	0.14
Consists of interlaminated dark grey to black mudstone and light to medium grey chert. Regionally, a 1m thick graptolite zone occurs 15m below the top of the upper unit, this is usable as a horizon. The USMS is divided into 3 units. The Lower Unit contains abundant limestone concretions and Galena and sphalerite micro-concretions occur locally near the base of this unit. Atypically calcareous locally « gra , lm chrt -20.00% », « cg xtl sph crns ca 5.00-20.00cm », « bed chrt 10.00-15.00% », « 124.20- 192.80 Moderately to strongly calcareous; calcite veins throughout; no concretions »			631153	154.00	154.40	0.40	0.35	4.58	5.00	110.00	0.08
			631154	154.40	154.90	0.50	0.05	0.15	1.00	5.00	0.33
			631155	214.80	216.10	1.30	0.05	0.18	1.00	5.00	0.28
			631156	216.10	216.60	0.50	0.04	0.12	1.00	5.00	0.33
			631157	216.60	218.20	1.60	0.39	0.30	1.00	10.00	1.30
			631158	218.20	219.80	1.60	0.04	0.02	1.00	5.00	2.00
			631159	219.80	221.60	1.80	1.09	0.93	2.00	20.00	1.17
			631160	221.60	223.30	1.70	0.09	0.21	1.00	5.00	0.43
			631161	221.60	223.30	1.70	0.26	0.39	1.00	10.00	0.67
			631162	223.30	225.20	1.90	1.02	3.22	3.00	100.00	0.32
< @ 132.20 s0 tca 66° >											

Selwyn Project Diamond Drill Log

Hole Number:
XYC-193

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
< @ 141.90 s0 tca 69° > « 153.60- 154.00 Active Member range: medium grey laminated calcareous mudstone; NITON: 11.6% Zn; 4.1 % Pb » « 154.00- 154.40 Breccia and gouge-rich fault » < @ 158.30 s0 tca 54° > < @ 165.20 so tca 50° > < @ 181.90 so tca 50° > < @ 191.10 s0 tca 77° > « 203.20- 203.80 light grey laminated mudstone; NITON: ~0.05% Zn » « 214.80- 216.10 cherty mudstone with no visible mineralization; NITON: 0.1-0.2% Zn » « 216.10- 216.60 cherty mudstone, light grey; NITON: 0.1-0.2% Zn, 0-0.2% Pb » « 216.60- 225.20 NITON: 0.5-1.5% combined » « flt »											
225.20	231.80	ACTM	631163	225.20	225.50	0.30	3.62	7.55	3.00	260.00	0.48
ACTM – Active Member			631164	225.50	226.00	0.50	11.35	21.44	6.00	960.00	0.53
			631165	226.00	226.50	0.50	9.32	24.24	6.00	1010.00	0.38
The ACTM consists of a repetitive, possibly rhythmic, sequence of intercalated carbonaceous mudstone, cherty mudstone, chert and limestone and locally contains economically significant Zn and Pb sulphides (see bold marked facies), mainly in its sections with well developed lamination. Because of its heterogeneity, the member is distinctive and easily identified. =====			631166	226.50	226.90	0.40	6.74	21.66	4.00	820.00	0.31
			631167	226.90	227.70	0.80	0.64	3.54	1.00	100.00	0.18
			631168	227.70	228.90	1.20	0.15	0.03	1.00	5.00	5.00
			631169	228.90	230.00	1.10	0.44	0.24	1.00	5.00	1.83
			631170	230.00	230.00	0.00	0.03	0.01	1.00	5.00	6.00
			631171	230.00	231.20	1.20	0.17	0.33	1.00	10.00	0.52
			631172	231.20	231.80	0.60	0.09	0.06	1.00	5.00	1.50

Selwyn Project Diamond Drill Log

Hole Number:
XYC-193

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		The ACTM has 8 different facies: ===== - GREY CHERT FACIES: Consists of laminated medium light grey to medium dark grey chert. Mineralization: 95-99% quartz and up to 5% secondary calcite. - WHITISH GREY ZN-PB MUDSTONE FACIES: Is a laminated cherty rock containing up to 70% sulphides. Mineralization: quartz, sphalerite and galena are the major minerals with only minor amounts of pyrite and locally calcite. Sedimentary diagenetic structures are common and well displayed in the facies, such as: lamination, pseudo-beds, calcite nodules & limestone nodules and abundant water escape structures. Most obvious structure in facies is cross-cutting veins containing massive sphalerite and galena with minor pyrite. They range in width from 0.5 to 10mm. - THIN BEDDED CHERTY MUDSTONE FACIES: Consists of rhythmic intercalated laminae of chert, carbonaceous mudstone and minor micrite. This facies contains significant amounts of Zn and Pb sulphides. - CHERTY MUDSTONE FACIES: Consists of a greyish black monotonous siliceous, carbonaceous mudstone. It is most typically found overlying the thin bedded calcareous mudstone facies. - THIN BEDDED CALCAREOUS MUDSTONE FACIES: Consists of laminated carbonaceous mudstone containing 20-40% calcite, 40-55% quartz and 10-20% muscovite. Sulphides occur in laminae. In the XY area it is usually the lowest facies in the section to contain laminated sulphides. - CALCAREOUS MUDSTONE FACIES: Consists of grey to greyish black monotonous, calcareous siliceous carbonaceous mudstone. There are no feathery calcite beds or pyrite-calcite blebs in the facies, making it easily distinguishable from the CCMS.									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-193

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		- GRADED LIMESTONE FACIES: Is a laminated argillaceous limestone with intercalated carbonaceous limestone laminae. The main rock type in the facies is laminated limestone with laminae up to 0.1-7mm thick. - LIGHT GREY BASAL LIMESTONE FACIES - LGLS: Consists of laminated argillaceous limestone. In the Anniv area it marks the end of the ACTM. It's not always present in the stratigraphy. - BASAL FACIES: This is a highly contorted and locally foliated carbonaceous mudstone. Unlike the other facies it is not repeated higher in the member. It appears locally to contain the slip zone of a major slump. The facies has only been observed in the YX area. It is 0.1-2m thick. The facies consists of massive carbonaceous siliceous mudstone with lenses and laminae of contorted, slightly carbonaceous chert. This Active Member intersection is extremely faulted and broken-up throughout « 225.20- 225.50 Calcareous mudstone with limestone; mod visible mineralization; low hardness due to fault - crumbles easily ; NITON: 4.6% Zn, 5.2% Pb. » « 225.50- 226.90 Lt. grey calc mdst - lam'd; gal. veinlettes, sph nodules absent; spaced cleavage absent; low hardness; NITON unrealistic - est: 20% Zn, 15% Pb » « 226.90- 228.90 fault: limestone and calcareous mudstone fragments »« No visible mineralization; NITON: 0.55% Zn, 0.40% Pb » « 228.90- 230.00 fault; primarily limestone breccia »« NITON: 0.56% Zn, 0.53% Pb » « 230.00- 231.20 Fault - calcareous mudstone breccia »« NITON: 0.53% Zn, 0.47% Pb »									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-193

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		« 231.20- 231.80 Light grey laminated limestone; NITON: nil »									
231.80	279.50	CCMS	631173	231.80	235.00	3.20	0.35	0.89	3.00	30.00	0.39
		CCMS – Calcareous Mudstone	631174	235.00	236.10	1.10	0.04	0.14	2.00	5.00	0.29
			631175	236.10	237.20	1.10	0.04	0.08	2.00	5.00	0.50
			631176	237.20	238.30	1.10	0.04	0.02	3.00	5.00	2.00
		Massive, calcareous, carbonaceous, dark grey mudstone. Most of the member is massive, but rare poorly defined bedding and pyrite-calcite micro-concretions are present. Most diagnostic structures are feathery calcite beds (=thin calcite-cemented concretions, many of them contain pyrite cores) and calcite pseudo-beds (= fibrous calcite vein parallel to bedding).									
		« lm ca 5.00-10.00mm », « nodules py -3.00% 2.00-20.00mm »,									
		« 231.80- 236.80 fault - abundant gouge and breccia »« NITON: 0-1 % combined »									
		« 236.80- 251.40 very broken-up »									
		< @ 240.00 s0 tca 70° >									
		< @ 248.70 s0 tca 77° >									
		< @ 255.00 s0 tca 77° >									
		< @ 273.50 s0 tca 74° >									
279.50	279.50	EOH									

Diamond Drill Log

Comprehensive Report for Hole:

XYC-192

Hole No.: XYC-192	Depth: 450.50 m	Horizontal Length: 0.00 m	Project: 1710
Location Data:			
Property:	Selwyn Project	Claim Name:	X 11
Mining District:	Selwyn Basin	Grant Number:	Y64536
Province/Territory:	Yukon		
UTM Co-Ordinates & Altitude of Drill Hole Collar:			
UTM Easting:	488542.89 m	True Azimuth:	185.0 °
UTM Northing:	6926580.63 m	Hole Angle:	-76.5 °
Elevation (m):	1611.88 m	NTS Name:	Placer Creek
		NTS Number:	105I06
Grid Co-Ordinates of Drill Hole Collar:			
Grid Easting (m):	0.00 m	Grid Name:	HP 06
Grid Northing (m):	0.00 m	Grid Type:	100m
Grid Azimuth:	245.0 °		
Dimond Drilling Contract:			
Drilled By:	NL-01	Date Drilling Start:	07/06/2010
		Date Finish:	07/17/2010
Diamond Drill Core:			
Logged By:	Jelle De Bruyckere	Date Logging Start:	07/09/2010
		Date Finish:	07/14/2010
Legend for Core Logging Codes: PAX			
Core Size:	NQ3	Cemented:	Yes
Casing Depth:	6.20 m	Casing Pulled:	Yes
Water Depth:	0.00 m	Overburden Depth:	6.20 m
Level:		Section:	
		Drift:	

Selwyn Project

Diamond Drill Log

Survey Data for Hole

XYC-192

Hole Comments:

Wed, Jul 07 --- Lost water return several times, 20 feet of casing

=====

Thu, Jul 08 --- Lost the water several times, returning to normal now. Bioturbations present in narrow intervals.

=====

Fri, Jul 09 --- Hard rock, slow and good drilling, FLMD @ 380feet

=====

Sat, Jul 10 --- We're in USMS right now, at a total depth of 189.3m. Day shift drilled 120' and night shift drilled 80'. The BSSM-FLMD contact was at 65.7m. The FLMD-USMS contact is at 141.0m. Drilling is going well, core is pretty competent. No mechanical problems to mention.

=====

Sun, Jul 11 --- In ACTM at the moment. Total depth at morning shift change is 228.9m. DS drilled 80', NS drilled 50'. The USMS/ACTM contact is at 629' (191.7m). Starting from 146.0m the core becomes a bit blocky. From 191.1m it becomes even more blocky and faulted. So far I did not see any HG sections, only a few 20-40cm long sections of up to 8% Zn and up to 5% Pb. Fair amount of fault gauge within the ACTM.

=====

Mon, Jul 12 --- In CCMS at the moment. Total depth at morning shift change was 262.4m. DS drilled 70', NS drilled 40'. The core is blocky, with on average 3-5% fault gauge. No mechanical problems to mention.

=====

Tue, Jul 13 --- Still in CCMS. Total depth at morning shift change was 294m. DS drilled 80', NS drilled 23'. Core is still blocky with regularly a seam of fault gauge in it. NS spent 4 hrs fixing an exhaust problem at the engine's manifold. Al's stint is done. Kyle will take over night shift now.

=====

Wed, Jul 14 --- Still in CCMS. Total depth at morning shift change was 323m. DS drilled 65', NS drilled 31'. Core is still blocky, with locally minor fault gauge.

=====

Thu, Jul 15 --- Still in CCMS. Total depth at morning shift change was 369m. DS and NS combined drilled 151' (46m). Core is less blocky. Still locally some fault gauge and broken sections. Drilling is going better, as complete runs are now possible.

=====

Fri, Jul 16 --- Possibly in PSMS right now, to be determined later on. But, around 406m core is siliceous and a slight increase in pyrite is noticed, with a few faint lenticular pyrite concretions defining a bedding tca of 30degrees. Total depth at morning shift change is 411m after having drilled 42m in the past 24hrs. Almost no sections with fault gauge and core is more competent than majority of core encountered in last few days.

=====

Sat, Jul 17 --- Still in CCMS. Total depth at morning shift change was 443.5m. DS drilled 62', NS drilled 44'. Core is again a bit more blocky and with flt gg. Mudstone is still calcareous, with siliceous sections in between. Minor pyrite was observed, in the shape of an 8mm thick band.

=====

Selwyn Project

Diamond Drill Log

Survey Data for Hole

XYC-192

Sun, Jul 18 --- XYC-192 got shut down around 1.30pm yesterday in CCMS at a depth of 450.5m. The hole was taksed at 870' and was cemented all the way up to 500'.

<i>Depth</i>	<i>Dip</i>	<i>Azimuth</i>
0.00	-76.5	185.0
24.70	-75.9	187.4
49.10	-74.7	191.2
73.50	-74.1	193.0
97.80	-73.7	194.0
122.20	-73.0	195.7
146.60	-72.3	198.3
171.00	-71.8	198.0
195.40	-71.0	198.4
222.80	-70.5	201.3
244.10	-70.3	201.5
268.50	-70.2	202.3
292.90	-69.4	207.0
317.30	-68.3	204.9
341.70	-68.0	208.0
366.10	-67.0	208.6
390.40	-66.0	208.4
414.80	-65.2	212.7
439.20	-64.5	214.7

Selwyn Project Diamond Drill Log

Hole Number:
XYC-192

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
0.00	6.20	OVBR									
6.20	65.70	BSSM									
BSSM – Backside Siliceous Mudstone Greyish black laminated chert and siliceous mudstone. Randomly-oriented to bedding-parallel bioturbation is common in the bottom of the unit. « lm chrt 75.00-95.00% », « btrb 0.10-2.00cm » « Classic BSSM in the vicinity of FLMD. Rich in bioturbations and Flaggy Mudstone appearing sections. Pyrite bands, chert concretions and calcite veins. » ◁ @ 7.90 S0 defined by faint parallel py bands S0 tca 40° ▷ ◁ @ 14.70 S0 defined by parallel py bands S0 tca 30° ▷ ◁ @ 24.60 S0 defined by parallel btrb S0 tca 37° ▷ « 30.20- 35.30 White, slightly bioturbated siltstone » « 35.30- 41.20 Bioturbated mudstone » ◁ @ 40.00 S0 defined by parallel bioturbations S0 tca 46° ▷ ◁ @ 40.20 S0 defined by parallel bioturbations S0 tca 40° × @ 40.20 Beta 262° ▷ « 41.20- 43.90 Calcareous thinly bedded mudstone » ◁ @ 43.30 S0 defined by thin beds S0 tca 40° ▷ « 43.90- 62.30 Carbonaceous siliceous mudstone »											

Selwyn Project Diamond Drill Log

Hole Number:
XYC-192

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
« 62.30-	64.40	Calcareous mudstone. Increase in calcite veins. Some carbonate bands. »									
65.70	141.00	FLMD									
FLMD – Flaggy Mudstone Formation											
Dark grey mudstone in the upper portions of the unit grading into light grey mudstone to siltstone. Contains abundant wispy bioturbation which ranges from randomly-oriented at the top of the unit to bedding-parallel throughout the majority of the unit. Darker upper section has a strong fetid odour along broken surfaces. « btrb 0.10-2.00cm », « cg xtl crns ca 1.00-5.00% 5.00-150.00cm », « crns py 1.00-5.00% 0.10-0.50mm »											
« Classic FLMD. Grey to light grey siliceous bioturbated mudstone. Pyrite concretions (some with calcite rims) occur throughout. »											
‹ @ 107.10 S0 defined by parallel bioturbations S0 tca 26° ›											
‹ @ 117.50 S0 defined by parallel bioturbations S0 tca 35° ›											
‹ @ 127.50 S0 defined by parallel bioturbations S0 tca 37° ›											
« 105.80- 114.30 Increase in quartz veining. Core more broken up. »« flt gg 2%»« bx 4%»											
« 114.30- 114.80 bx 100%»											
‹ @ 139.80 S0 defined by parallel bioturbations S0 tca 43° ›											
141.00	191.70	USMS	631655	190.50	191.70	1.20	0.01	0.02	1.00	5.00	0.50
USMS – Upper Siliceous Mudstone											
Consists of interlaminated dark grey to black mudstone and light to medium grey chert. Regionally, a 1m thick graptolite zone occurs 15m below the top of the											

Selwyn Project Diamond Drill Log

Hole Number:
XYC-192

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		upper unit, this is usable as a horizon. The USMS is divided into 3 units. The Lower Unit contains abundant limestone concretions and Galena and sphalerite micro-concretions occur locally near the base of this unit. « gra , lm chrt -20.00% », « cg xtl sph crns ca 5.00-20.00cm », « bed chrt 10.00-15.00% » « Classic USMS: chert bands, carbonate bands, banded carbonate concretions and radiating carbonate concretions » ◁ @ 146.40 S0 defined by parallel pyrite bands S0 tca 42° ▷ ◁ @ 147.50 Appearance of the first chert bands ▷ ◁ @ 149.00 S0 defined by parallel pyrite bands S0 tca 35° ▷ ◁ @ 153.00 S0 defined by pyrite band, parallel to chert bands S0 tca 33° ▷ ◁ @ 160.00 S0 defined by carbonate band, parallel to chert bands S0 tca 49° ▷ ◁ @ 181.80 S0 defined by chert band S0 tca 54° ▷									
191.70	223.30	ACTM	631656	191.70	192.30	0.60	0.16	6.20	4.00	150.00	0.03
ACTM – Active Member			631657	192.30	193.40	1.10	0.37	7.55	4.00	180.00	0.05
			631658	193.40	194.30	0.90	0.03	0.24	1.00	5.00	0.13
The ACTM consists of a repetitive, possibly rhythmic, sequence of intercalated carbonaceous mudstone, cherty mudstone, chert and limestone and locally contains economically significant Zn and Pb sulphides (see bold marked facies), mainly in its sections with well developed lamination. Because of its heterogeneity, the member is distinctive and easily identified.			631659	194.30	195.10	0.80	0.03	0.63	1.00	20.00	0.05
			631660	195.10	195.50	0.40	2.47	11.35	4.00	400.00	0.22
			631661	195.10	195.50	0.40	2.53	12.97	3.00	470.00	0.20
			631662	195.50	195.75	0.25	0.88	1.32	3.00	50.00	0.67
			631663	195.75	195.90	0.15	0.05	1.27	1.00	30.00	0.04
			631664	195.90	196.90	1.00	0.01	0.16	2.00	5.00	0.06
=====			631665	196.90	197.90	1.00	0.01	0.01	3.00	5.00	2.00
The ACTM has 8 different facies:			631666	197.90	199.20	1.30	0.01	0.01	1.00	5.00	2.00
=====			631667	199.20	200.30	1.10	0.01	0.01	1.00	5.00	2.00
			631668	200.30	200.90	0.60	0.01	0.05	1.00	5.00	0.20

Selwyn Project Diamond Drill Log

Hole Number:
XYC-192

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
- GREY CHERT FACIES: Consists of laminated medium light grey to medium dark grey chert. Mineralization: 95-99% quartz and up to 5% secondary calcite. - WHITISH GREY ZN-PB MUDSTONE FACIES: Is a laminated cherty rock containing up to 70% sulphides. Mineralization: quartz, sphalerite and galena are the major minerals with only minor amounts of pyrite and locally calcite. Sedimentary diagenetic structures are common and well displayed in the facies, such as: lamination, pseudo-beds, calcite nodules & limestone nodules and abundant water escape structures. Most obvious structure in facies is cross-cutting veins containing massive sphalerite and galena with minor pyrite. They range in width from 0.5 to 10mm. - THIN BEDDED CHERTY MUDSTONE FACIES: Consists of rhythmic intercalated laminae of chert, carbonaceous mudstone and minor micrite. This facies contains significant amounts of Zn and Pb sulphides. - CHERTY MUDSTONE FACIES: Consists of a greyish black monotonous siliceous, carbonaceous mudstone. It is most typically found overlying the thin bedded calcareous mudstone facies. - THIN BEDDED CALCAREOUS MUDSTONE FACIES: Consists of laminated carbonaceous mudstone containing 20-40% calcite, 40-55% quartz and 10-20% muscovite. Sulphides occur in laminae. In the XY area it is usually the lowest facies in the section to contain laminated sulphides. - CALCAREOUS MUDSTONE FACIES: Consists of grey to greyish black monotonous, calcareous siliceous carbonaceous mudstone. There are no feathery calcite beds or pyrite-calcite blebs in the facies, making it easily distinguishable from the CCMS. - GRADED LIMESTONE FACIES: Is a laminated argillaceous limestone with intercalated carbonaceous limestone laminae. The main rock type in the facies is laminated limestone with laminae up to 0.1-7mm thick.			631669	200.90	201.10	0.20	0.66	0.78	1.00	30.00	0.85
			631670	201.10	201.10	0.00	0.01	0.01	1.00	5.00	2.00
			631671	201.10	202.70	1.60	0.04	0.09	2.00	10.00	0.44
			631672	202.70	203.70	1.00	1.39	7.22	6.00	270.00	0.19
			631673	203.70	203.80	0.10	5.30	15.78	4.00	710.00	0.34
			631674	203.80	204.50	0.70	3.44	13.99	4.00	660.00	0.25
			631675	204.50	205.80	1.30	1.95	1.64	3.00	90.00	1.19
			631676	205.80	206.80	1.00	1.27	4.09	3.00	230.00	0.31
			631677	206.80	207.80	1.00	0.62	2.09	1.00	70.00	0.30
			631678	207.80	208.40	0.60	0.21	14.26	6.00	340.00	0.01
			631679	208.40	208.90	0.50	0.17	1.83	1.00	50.00	0.09
			631680	208.90	208.90	0.00	6.16	7.02	70.00	180.00	0.88
			631681	208.90	210.40	1.50	0.18	0.61	1.00	10.00	0.30
			631682	210.40	210.90	0.50	3.64	17.01	9.00	470.00	0.21
			631683	210.90	212.50	1.60	0.54	0.43	3.00	10.00	1.26
			631684	212.50	213.70	1.20	0.01	0.02	1.00	5.00	0.50
			631685	213.70	215.20	1.50	0.01	0.01	2.00	5.00	2.00
			631686	215.20	216.70	1.50	0.01	0.01	1.00	5.00	2.00
			631687	216.70	218.20	1.50	0.01	0.01	3.00	5.00	1.00
			631688	218.20	219.50	1.30	0.07	0.26	3.00	5.00	0.27
			631689	219.50	220.60	1.10	0.37	0.83	5.00	30.00	0.45
			631690	220.60	221.60	1.00	0.30	0.60	3.00	20.00	0.50
			631691	220.60	221.60	1.00	0.63	0.73	5.00	20.00	0.86
			631692	221.60	222.80	1.20	0.02	0.01	1.00	5.00	4.00
			631693	222.80	223.30	0.50	0.01	0.01	1.00	5.00	2.00

Selwyn Project Diamond Drill Log

Hole Number:
XYC-192

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		- <i>LIGHT GREY BASAL LIMESTONE FACIES - LGLS: Consists of laminated argillaceous limestone. In the Anniv area it marks the end of the ACTM. It's not always present in the stratigraphy.</i> - <i>BASAL FACIES: This is a highly contorted and locally foliated carbonaceous mudstone. Unlike the other facies it is not repeated higher in the member. It appears locally to contain the slip zone of a major slump. The facies has only been observed in the YX area. It is 0.1-2m thick. The facies consists of massive carbonaceous siliceous mudstone with lenses and laminae of contorted, slightly carbonaceous chert.</i> « 191.70- 193.40 Siliceous mudstone with limestone concretions. The mudstone has moderately to well developed lamination. Sphalerite + Ga present. Mineralization: 6% Zn & 0.5% Pb. Rich in pyrite. » « 193.40- 194.30 Limestone with a moderately developed bedding » « @ 194.50 S0 tca 27° » « @ 194.50 Beta (top mark was questionable) 288° » « 194.30- 195.10 Siliceous mudstone. Broken core. Low to no mineralization. » « 195.10- 195.50 Siliceous mudstone rich in calcite veining and pyrite. Average mineralization: 5.7% Zn & 3.3% Pb. » « 195.50- 195.75 Calcareous barren mudstone rich in calcite. » « 195.75- 195.90 Siliceous mudstone. Rich in pyrite. Very low mineralization: 0.5% Zn » « 195.90- 200.30 Grey Chert Facies. Brecciated. Lots of calcite veining. Pyrite present. No mineralization. »									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-192

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		« 200.30- 200.90 Siliceous mudstone. Rich in chert. More carbonaceous. No mineralization. »									
		« 200.90- 201.10 Calcareous mudstone. Rich in calcite. Low mineralization: 0.2% Zn & 0.4% Pb »									
		« 201.10- 202.70 Broken up section. Calcareous and siliceous sections. No mineralization. »									
		« 202.70- 203.70 Siliceous mudstone with overall well developed lamination. Mineralization: 5.5% Zn & 2.7% Pb »									
		« 203.70- 203.80 Whitish Grey Zn-Pn Mudstone Facies. Mineralization: 20% Zn & 12% Pb »									
		« 203.80- 204.50 Siliceous mudstone + partially Whitish Grey Zn-Pb Mudstone Facies. Mineralization: 9% Zn & 5% Pb »									
		« 204.50- 207.80 Siliceous mudstone. Broken up. »« flt gg 25%»									
		« 207.80- 208.50 Badly broken core. Mineralization: 10% Zn & 1% Pb. »« flt gg 30°»									
		« 208.40- 208.90 Badly broken core. Low to no mineralization »									
		« 208.90- 210.40 Siliceous mudstone. Rich in calcite veining. Broken up. No mineralization. »									
		« 210.40- 210.90 Siliceous mudstone with limestone concretions. The mudstone shows well developed laminations. Mineralization: 10% Zn & 4% Pb »									
		« 210.90- 212.50 Limestone. Could be the basal limestone, because the next 19.1m looks like footwall rocks. BUT, one galena bleb (30mm long, 3mm wide) was noticed just before the limestone section (221.6m-223.3m). »									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-192

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		« 212.50- 221.60 Siliceous carbonaceous barren mudstone. One galena bleb (30mm long, 3mm wide) at 221.2m » « 221.60- 223.30 Basal light grey limestone »									
223.30	450.50	CCMS	631694	223.30	224.00	0.70	0.01	0.01	1.00	5.00	2.00
CCMS – Calcareous Mudstone			631651	244.30	244.45	0.15	0.01	0.54	3.00	50.00	0.02
Massive, calcareous, carbonaceous, dark grey mudstone. Most of the member is massive, but rare poorly defined bedding and pyrite-calcite micro-concretions are present. Most diagnostic structures are feathery calcite beds (=thin calcite-cemented concretions, many of them contain pyrite cores) and calcite pseudo-beds (= fibrous calcite vein parallel to bedding). « lm ca 5.00-10.00mm », « nodules py -3.00% 2.00-20.00mm » « 223.30- 450.50 Massive, calcareous, carbonaceous dark grey to almost black mudstone. Core is blocky, contains local thin sections of fault gauge. Core is dominantly broken along bedding. Minor pyrite concretions (with quartz + calcite rims) are present. Rare poorly defined bedding was observed. Feathery calcite beds parallel to bedding is present. » « @ 241.60 S0 defined by faint bed S0 tca 43° » « 244.30- 244.45 Siliceous mudstone with calcite veins containing minor Zn (2%), no Pb. » « 244.75- 244.85 Siliceous mudstone with calcite veins containing minor Zn (0.8%), no Pb. » « 245.30- 245.55 Calcareous mudstone containing minor Zn (0.5%), no Pb. » « 262.55- 262.70 Calcareous mudstone containing minor Zn (0.4%), no Pb.			631652	244.75	244.85	0.10	0.01	1.11	4.00	90.00	0.01
			631653	245.30	245.55	0.25	0.01	0.38	1.00	40.00	0.03
			631654	262.55	262.70	0.15	0.01	0.44	1.00	40.00	0.02

Selwyn Project Diamond Drill Log

Hole Number:
XYC-192

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
»											
◁ @ 264.10 S0 defined by faint bed of disseminated pyrite S0 tca 53° ▷											
◁ @ 273.80 S0 defined by feathery calcite veins S0 tca 53° ▷											
◁ @ 308.70 S0 defined by faint bed S0 tca 42° ▷											
◁ @ 371.10 Minor increase of pyrite in core. Core is significantly more competent from this point on. Still calcareous mudstone. ▷											
◁ @ 372.40 S0 defined by a feathery calcite bed S0 tca 28° ▷											
◁ @ 381.70 S0 defined by very faint bedding S0 tca 34° ▷											
« 388.20- 389.50 Section of siliceous mudstone. Minor pyrite. »											
« 395.70- 396.60 Section of siliceous mudstone. Minor pyrite. »											
◁ @ 406.70 S0 defined by a few faint lenticular pyrite concretions parallel to bedding S0 tca 30° ▷											
◁ @ 413.30 S0 defined by a bed of pyrite concretions + quartz S0 tca 31° ▷ @ 395.70 Beta 193° ▷											
◁ @ 417.20 S0 defined by a bed of pyrite concretions + quartz S0 tca 32° ▷											
◁ @ 447.90 S0 defined by very faint beds of finely disseminated pyrite S0 tca 37° ▷											
◁ @ 428.60 S0 defined by calcite pseudo-bed S0 tca 28° ▷ @ 428.60 Beta 174° ▷											
450.50	450.50	EOH									

Diamond Drill Log

Comprehensive Report for Hole:

XYC-191

Hole No.: XYC-191	Depth: 175.30 m	Horizontal Length: 0.00 m	Project: 1710
Location Data:			
Property:	Selwyn Project	Claim Name:	X 11
Mining District:	Selwyn Basin	Grant Number:	Y64536
Province/Territory:	Yukon		
UTM Co-Ordinates & Altitude of Drill Hole Collar:			
UTM Easting:	488331.44 m	True Azimuth:	185.0 °
UTM Northing:	6926618.55 m	Hole Angle:	-67.0 °
Elevation (m):	1558.55 m	NTS Name:	Placer Creek
		NTS Number:	105I06
Grid Co-Ordinates of Drill Hole Collar:			
Grid Easting (m):	0.00 m	Grid Name:	HP 06
Grid Northing (m):	0.00 m	Grid Type:	100m
Grid Azimuth:	245.0 °		
Dimond Drilling Contract:			
Drilled By:	NL-01	Date Drilling Start:	07/01/2010
		Date Finish:	07/06/2010
Diamond Drill Core:			
Logged By:	Jelle De Bruyckere	Date Logging Start:	07/05/2010
		Date Finish:	07/08/2010
Legend for Core Logging Codes: PAX			
Core Size:	NQ3	Cemented:	Yes
Casing Depth:	12.20 m	Casing Pulled:	Yes
Water Depth:	0.00 m	Overburden Depth:	12.20 m
Level:			
Section:		Drift:	

Selwyn Project

Diamond Drill Log

Survey Data for Hole

XYC-191

Hole Comments:

Fri, Jul 02 --- move to set-up in the afternoon, heavy rain last night one corner of the drill sunk in soft ground. Collared in FLMD,

=====

Sat, Jul 03 --- lost water return a few times, not doing full runs, contact FLMD/USMS at 220 feet and fault starts at 235 feet

=====

Sun, Jul 04 --- Very blocky, AM starts at 271 feet, still in AM at end of night shift. I am not sure the core will be oriented core is broken-up and mushy.

=====

Mon, Jul 05 --- Still blocky, bad quality core.

=====

Tue, Jul 06 --- Shut down the hole @ 575', cemented to 220', moving to next set-up this morning

<i>Depth</i>	<i>Dip</i>	<i>Azimuth</i>
0.00	-67.0	185.0
24.70	-66.6	185.0
55.20	-66.1	184.5
73.50	-65.8	185.9
97.80	-65.8	188.0
121.90	-65.4	191.1
171.00	-64.6	193.8

Selwyn Project Diamond Drill Log

Hole Number:
XYC-191

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
0.00	12.20	OVBR									
12.20	68.70	FLMD									
<i>FLMD – Flaggy Mudstone Formation</i> <i>Dark grey mudstone in the upper portions of the unit grading into light grey mudstone to siltstone. Contains abundant wispy bioturbation which ranges from randomly-oriented at the top of the unit to bedding-parallel throughout the majority of the unit. Darker upper section has a strong fetid odour along broken surfaces. « btrb 0.10-2.00cm », « cg xtl crns ca 1.00-5.00% 5.00-150.00cm », « crns py 1.00-5.00% 0.10-0.50mm »</i> <i>« Classic FLMD. Grey siliceous mudstone with abundant pyrite concretions »</i> <i>« @ 15.60 S0 defined by parallel bioturbations - S0 tca 63° »</i> <i>« 32.50- 33.80 Calcareous laminated mudstone »</i> <i>« @ 32.90 S0 defined by parallel lamination - S0 tca 68° »</i> <i>« @ 46.70 S0 tca 42° »</i>											
68.70	75.40	USMS									
<i>USMS – Upper Siliceous Mudstone</i> <i>Consists of interlaminated dark grey to black mudstone and light to medium grey chert. Regionally, a 1m thick graptolite zone occurs 15m below the top of the upper unit, this is usable as a horizon. The USMS is divided into 3 units. The Lower Unit contains abundant limestone concretions and Galena and sphalerite micro-concretions occur locally near the base of this unit. « gra , lm chrt -20.00% », « cg xtl sph crns ca 5.00-20.00cm », « bed chrt 10.00-15.00% »</i> <i>« 71.20- 75.40 This section in the USMS is part of the fault, but USMS</i>											

Selwyn Project Diamond Drill Log

Hole Number:
XYC-191

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		is recognizable. »									
75.40	81.40	FLT	631251	80.50	81.40	0.90	0.03	0.09	1.00	4.00	0.33
		« None of the core within this section has recognizable stratigraphy. Because the fault has shortened the USMS unit drastically, it's logged separately to show up in the d_geol. »« flt gg 40%»« flt bx 40%»« brco 10%»									
81.40	168.10	ACTM	631252	81.40	83.00	1.60	0.11	0.49	1.00	20.00	0.22
		ACTM – Active Member	631253	83.00	84.60	1.60	1.58	4.87	3.00	210.00	0.32
			631254	84.60	85.50	0.90	1.76	7.25	2.00	210.00	0.24
		The ACTM consists of a repetitive, possibly rhythmic, sequence of intercalated carbonaceous mudstone, cherty mudstone, chert and limestone and locally contains economically significant Zn and Pb sulphides (see bold marked facies), mainly in its sections with well developed lamination. Because of its heterogeneity, the member is distinctive and easily identified.	631255	85.50	87.00	1.50	0.77	1.67	1.00	40.00	0.46
			631256	87.00	88.20	1.20	0.38	1.23	1.00	40.00	0.31
			631257	88.20	89.10	0.90	1.06	2.61	2.00	80.00	0.41
			631258	89.10	90.70	1.60	1.50	5.95	1.00	160.00	0.25
			631259	90.70	91.70	1.00	0.29	0.59	1.00	20.00	0.49
			631260	91.70	92.40	0.70	0.11	0.25	1.00	4.00	0.44
		=====	631261	91.70	92.40	0.70	0.19	0.56	1.00	20.00	0.34
		The ACTM has 8 different facies:	631262	92.40	92.90	0.50	4.21	14.93	4.00	450.00	0.28
		=====	631263	92.90	93.90	1.00	0.06	0.23	1.00	4.00	0.26
			631264	93.90	95.00	1.10	2.13	11.49	1.00	260.00	0.19
		- GREY CHERT FACIES: Consists of laminated medium light grey to medium dark grey chert. Mineralization: 95-99% quartz and up to 5% secondary calcite.	631265	95.00	96.20	1.20	0.34	1.74	1.00	40.00	0.20
			631266	96.20	96.90	0.70	0.49	1.92	1.00	60.00	0.26
			631267	96.90	97.40	0.50	5.43	7.03	3.00	320.00	0.77
		- WHITISH GREY ZN-PB MUDSTONE FACIES: Is a laminated cherty rock containing up to 70% sulphides. Mineralization: quartz, sphalerite and galena are the major minerals with only minor amounts of pyrite and locally calcite. Sedimentary diagenetic structures are common and well displayed in the facies, such as: lamination, pseudo-beds, calcite nodules & limestone nodules and abundant water escape structures. Most obvious structure in facies is cross-cutting veins containing massive sphalerite and galena with minor pyrite. They range in width from 0.5 to 10mm.	631268	97.40	97.60	0.20	0.11	0.45	1.00	20.00	0.24
			631269	97.60	98.10	0.50	1.01	4.22	3.00	140.00	0.24
			631270	98.10	98.10	0.00	0.01	0.01	1.00	4.00	2.00
			631271	98.10	98.70	0.60	0.01	0.02	1.00	4.00	0.50
			631272	98.70	99.30	0.60	0.18	0.22	2.00	4.00	0.82
			631273	99.30	99.60	0.30	0.01	0.01	1.00	4.00	2.00
			631274	99.60	100.40	0.80	0.01	0.07	1.00	4.00	0.14
			631275	100.40	103.90	3.50	0.04	0.06	1.00	4.00	0.67
			631276	103.90	104.50	0.60	2.26	7.43	3.00	210.00	0.30
			631277	104.50	106.00	1.50	0.69	1.46	1.00	50.00	0.47
		- THIN BEDDED CHERTY MUDSTONE FACIES: Consists of rhythmic intercalated laminae of chert, carbonaceous mudstone and minor micrite. This facies contains	631278	106.00	107.10	1.10	0.37	1.19	1.00	40.00	0.31

Selwyn Project Diamond Drill Log

Hole Number:
XYC-191

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
significant amounts of Zn and Pb sulphides.			631279	107.10	108.30	1.20	0.01	0.01	1.00	4.00	2.00
- <i>CHERTY MUDSTONE FACIES: Consists of a greyish black monotonous siliceous, carbonaceous mudstone. It is most typically found overlying the thin bedded calcareous mudstone facies.</i>			631280	108.30	108.30	0.00	0.94	1.29	219.00	80.00	0.73
			631281	108.30	109.50	1.20	1.03	7.52	2.00	270.00	0.14
			631282	109.50	110.60	1.10	1.23	4.04	1.00	130.00	0.30
			631283	110.60	110.90	0.30	5.38	23.65	8.00	750.00	0.23
- <i>THIN BEDDED CALCAREOUS MUDSTONE FACIES: Consists of laminated carbonaceous mudstone containing 20-40% calcite, 40-55% quartz and 10-20% muscovite. Sulphides occur in laminae. In the XY area it is usually the lowest facies in the section to contain laminated sulphides.</i>			631284	110.90	111.30	0.40	12.12	25.46	7.00	1080.00	0.48
			631285	111.30	111.90	0.60	8.23	22.45	7.00	790.00	0.37
			631286	111.90	112.20	0.30	6.29	25.07	5.00	770.00	0.25
- <i>CALCAREOUS MUDSTONE FACIES: Consists of grey to greyish black monotonous, calcareous siliceous carbonaceous mudstone. There are no feathery calcite beds or pyrite-calcite blebs in the facies, making it easily distinguishable from the CCMS.</i>			631287	112.20	113.10	0.90	1.18	4.63	2.00	130.00	0.25
			631288	113.10	114.10	1.00	1.11	5.92	3.00	160.00	0.19
			631289	114.10	114.60	0.50	2.05	9.10	4.00	270.00	0.23
			631290	114.60	115.30	0.70	6.32	16.90	4.00	630.00	0.37
- <i>GRADED LIMESTONE FACIES: Is a laminated argillaceous limestone with intercalated carbonaceous limestone laminae. The main rock type in the facies is laminated limestone with laminae up to 0.1-7mm thick.</i>			631291	114.60	115.30	0.70	7.58	19.83	6.00	740.00	0.38
			631292	115.30	115.70	0.40	8.21	22.40	7.00	900.00	0.37
			631293	115.70	118.10	2.40	0.21	1.06	1.00	40.00	0.20
			631294	118.10	118.90	0.80	0.26	0.17	1.00	4.00	1.53
- <i>LIGHT GREY BASAL LIMESTONE FACIES - LGLS: Consists of laminated argillaceous limestone. In the Anniv area it marks the end of the ACTM. It's not always present in the stratigraphy.</i>			631295	118.90	119.80	0.90	1.75	5.55	1.00	170.00	0.32
			631296	119.80	120.20	0.40	4.76	26.87	5.00	700.00	0.18
			631297	120.20	120.40	0.20	6.09	5.09	1.00	290.00	1.20
			631298	120.40	120.90	0.50	8.59	9.74	1.00	570.00	0.88
- <i>BASAL FACIES: This is a highly contorted and locally foliated carbonaceous mudstone. Unlike the other facies it is not repeated higher in the member. It appears locally to contain the slip zone of a major slump. The facies has only been observed in the YX area. It is 0.1-2m thick. The facies consists of massive carbonaceous siliceous mudstone with lenses and laminae of contorted, slightly carbonaceous chert.</i>			631299	120.90	122.00	1.10	1.57	2.07	1.00	100.00	0.76
			631300	122.00	122.00	0.00	0.04	0.04	1.00	4.00	1.00
			631301	122.00	122.50	0.50	3.95	0.89	1.00	40.00	4.44
			631302	122.50	123.10	0.60	6.89	9.14	1.00	460.00	0.75
			631303	123.10	123.70	0.60	10.57	17.29	3.00	840.00	0.61
			631304	123.70	124.00	0.30	8.33	13.69	2.00	690.00	0.61
			631305	124.00	125.00	1.00	0.11	0.12	1.00	4.00	0.92
			631306	125.00	126.20	1.20	0.19	0.08	1.00	4.00	2.38
			631307	126.20	126.80	0.60	14.76	19.21	4.00	1050.00	0.77
			631308	126.80	128.10	1.30	0.03	0.06	1.00	4.00	0.50
			631309	128.10	129.20	1.10	0.10	0.13	1.00	4.00	0.77
			631310	129.20	129.20	0.00	1.47	4.36	30.00	270.00	0.34
			631311	129.20	130.80	1.60	0.08	0.28	1.00	4.00	0.29

Selwyn Project Diamond Drill Log

Hole Number:
XYC-191

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
<i>Note: After 126.8m (last occurrence of high grade ACTM), the core contains low grade Zn & Pb throughout, up until the last 7m of the hole, which consists of 100% fault gouge. Having a 30mm diameter galena bleb, a 20cm galena stringer and sections of up to 2% Zn, Gabe and I (Jelle) concluded that this can not be footwall rocks.</i> « 81.40- 84.60 Siliceous carbonaceous mudstone. No Sphalerite or Galena mineralization. Three short (<10cm) calcareous sections with pyrite concretions. » « 84.60- 85.50 Siliceous mudstone with moderately developed lamination. Sphalerite and Galena present. Mineralization: 7% Zn & 3% Pb. » « 85.50- 89.10 Limestone » « @ 86.70 Mineral in the core containing 20% Ti and 15% V » « 89.10- 90.70 Same rock as the interval 84.6m-85.5m, but lower grade. Mineralization: 2.5% Zn & 1.0% Pb. Visible Galena concretions. » « 90.70- 92.40 Limestone » « 92.40- 92.90 Siliceous mudstone with well developed lamination. Sphalerite and Galena visible. Mineralization: 16% Zn & 8% Pb. » « 92.90- 93.90 Siliceous carbonaceous black mudstone with calcite veins and pyrite concretions. No mineralization. » « 93.90- 95.00 Light to dark grey mudstone with moderately developed lamination. Mineralization: 4.5% Zn & 1.5% Pb. » « 95.00- 96.20 Dark grey siliceous mudstone with faint moderately developed lamination. Mineralization: 1.5% Zn & 0.3% Pb. » « 96.20- 96.90 Calcareous mudstone without minor mineralization.: 1.7%			631312	130.80	132.00	1.20	0.04	0.01	1.00	4.00	8.00
			631313	132.00	133.00	1.00	0.02	0.01	1.00	4.00	4.00
			631314	133.00	133.80	0.80	0.07	0.19	1.00	4.00	0.37
			631315	133.80	134.10	0.30	0.08	0.59	2.00	20.00	0.14
			631316	134.10	135.00	0.90	0.21	0.35	4.00	10.00	0.60
			631317	135.00	135.10	0.10	0.12	1.90	6.00	60.00	0.06
			631318	135.10	136.60	1.50	0.82	1.67	8.00	50.00	0.49
			631319	136.60	138.10	1.50	0.06	1.68	6.00	60.00	0.04
			631320	138.10	139.30	1.20	0.04	0.11	3.00	4.00	0.36
			631321	138.10	139.30	1.20	0.04	0.30	4.00	4.00	0.13
			631322	139.30	139.80	0.50	0.15	0.67	3.00	20.00	0.22
			631323	139.80	141.20	1.40	0.41	1.19	4.00	30.00	0.34
			631324	141.20	141.50	0.30	0.26	1.47	1.00	30.00	0.18
			631325	141.50	143.00	1.50	0.20	1.93	4.00	50.00	0.10
			631326	143.00	144.50	1.50	0.02	0.01	1.00	4.00	4.00
			631327	144.50	145.80	1.30	0.02	0.01	1.00	4.00	4.00
			631328	145.80	147.30	1.50	0.02	0.01	1.00	4.00	4.00
			631329	147.30	148.70	1.40	0.03	0.01	1.00	4.00	6.00
			631330	148.70	148.70	0.00	0.01	0.01	2.00	4.00	2.00
			631331	148.70	150.10	1.40	0.13	0.01	3.00	4.00	26.00
			631332	150.10	150.30	0.20	10.68	1.62	20.00	40.00	6.59
			631333	150.30	151.90	1.60	0.32	1.58	2.00	40.00	0.20
			631334	151.90	152.30	0.40	0.18	1.21	2.00	30.00	0.15
			631335	152.30	152.40	0.10	0.19	0.11	3.00	4.00	1.73
			631336	152.40	152.70	0.30	0.23	1.59	3.00	40.00	0.14
			631337	152.70	152.90	0.20	0.44	0.71	3.00	20.00	0.62
			631338	152.90	153.30	0.40	0.21	2.02	3.00	50.00	0.10
			631339	153.30	153.50	0.20	0.08	0.37	2.00	4.00	0.22
			631340	153.50	153.50	0.00	0.92	1.27	211.00	80.00	0.72
			631341	153.50	154.00	0.50	0.75	1.15	3.00	30.00	0.65
			631342	154.00	154.50	0.50	0.30	0.48	3.00	10.00	0.63
			631343	154.50	154.70	0.20	0.39	0.38	3.00	4.00	1.03
			631344	154.70	154.95	0.25	0.03	0.04	2.00	4.00	0.75
			631345	154.95	155.10	0.15	0.17	1.91	1.00	50.00	0.09
			631346	155.10	155.30	0.20	0.09	1.62	2.00	40.00	0.06

Selwyn Project Diamond Drill Log

Hole Number:
XYC-191

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		Zn. A 20cm thick calcite vein is present. »	631347	155.30	155.80	0.50	0.79	1.00	4.00	30.00	0.79
		« 96.90- 97.40 Siliceous mudstone with a well developed lamination. Locally (over 5cm) 20% Zn. Mineralization: 6% Zn & 3% Pb. »	631348	155.80	156.90	1.10	0.63	1.24	4.00	30.00	0.51
			631349	156.90	158.30	1.40	0.06	0.35	2.00	4.00	0.17
			631350	158.30	159.60	1.30	0.09	0.51	1.00	10.00	0.18
		« 97.40- 97.60 Limestone »	631351	158.30	159.60	1.30	0.06	0.87	1.00	20.00	0.07
			631352	159.60	160.80	1.20	0.11	1.02	1.00	20.00	0.11
		« 97.60- 98.10 Siliceous mudstone with a well developed lamination. Mineralization: 10% Zn & 4% Pb. »	631353	160.80	161.20	0.40	0.05	0.23	1.00	4.00	0.22
			631354	161.20	162.80	1.60	0.26	1.09	1.00	30.00	0.24
			631355	162.80	164.20	1.40	0.15	0.15	1.00	4.00	1.00
		« 98.10- 98.70 Limestone»	631356	164.20	164.80	0.60	0.13	0.24	1.00	4.00	0.54
			631357	164.80	165.90	1.10	0.13	0.40	1.00	10.00	0.33
		« 98.70- 103.90 Barren siliceous mudstone. Pretty badly broken up. »	631358	165.90	167.20	1.30	0.22	1.74	3.00	50.00	0.13
			631359	167.20	167.80	0.60	0.15	0.13	1.00	4.00	1.15
		« 103.90- 104.50 Siliceous mudstone with an average mineralization of 4% Zn & 1% Pb. »	631360	167.80	167.80	0.00	0.01	0.01	1.00	4.00	2.00
			631361	167.80	168.10	0.30	0.19	1.18	3.00	40.00	0.16
		« 104.50- 107.10 Limestone »									
		« 107.10- 110.60 Mainly flt gg + flt bx »									
		« 110.60- 112.20 Massive sulphides, high grade ore. Whitish Grey Zn-Pb Mudstone Facies. Sphalerite crystals visible. Mineralization: 20% Zn & 15% Pb. »									
		« 112.20- 114.10 Calcareous mudstone with no lamination. Low mineralization: 4.2% Zn & 1.2% Pb. »									
		« 114.10- 114.60 Flt gg + flt bx. But also mineralized: 14% Zn & 7% Pb. »									
		« 114.60- 115.70 Massive sulphides, high grade ore. Whitish Grey Zn-Pn Mudstone Facies. Mineralization: 20% Zn & 15% Pb. Sphalerite crystals are visible. »									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-191

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		« 115.70- 118.10 Flt gg + flt bx + brco of limestone »									
		« 118.10- 119.80 Mainly limestone »									
		« 119.80- 120.20 Massive sulphides, high grade ore. Still competent core, but affected by faulting. Mineralization: 20% Zn & 10% Pb. »									
		« 120.20- 120.40 Limestone with minor mineralization: 2% Zn & 2% Pb »									
		« 120.40- 120.90 Massive sulphides, high grade ore. Whitish Grey Zn-Pb mudstone facies. Mineralization: 22% Zn & 15% Pb. »									
		« 120.90- 122.00 Calcareous mudstone with low mineralization: 2% Zn & 2% Pb. »									
		« 122.00- 122.50 Calcareous mudstone with no significant mineralization, except for 1 nice Galena concretion with a diameter of 2-3cm. »									
		« 122.50- 124.00 Massive sulphides, high grade ore. Whitish Grey Zn-Pn Mudstone Facies. Mineralization: 22% Zn & 15% Pb. »									
		« 124.00- 126.20 Calcareous mudstone with no mineralization »									
		« 126.20- 126.80 Massive sulphides. High grade ore. Whitish Grey Zn-Pn Mudstone Facies. Mineralization: 20% Zn & 15% Pb. »									
		« 126.80- 133.80 Barren section. No mineralization: Mostly calcareous mudstone, the rest is siliceous mudstone. »									
		« 133.80- 134.10 Calcareous mudstone with minor calcite veining and minor disseminated pyrite. Only weakly mineralized: 0.5% Zn & 0.5% Pb. »									
		« 134.10- 135.00 Barren calcareous mudstone with minor quartz/calcite veining and minor pyrite. »									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-191

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		« 135.00- 135.10 Same calcareous mudstone as above with 1% Zn and 0.4% Pb. »									
		« 135.10- 139.30 Black siliceous to locally faintly calcareous mudstone. Barren. »									
		« 139.30- 139.80 Monotonous calcareous mudstone with minor quartz/calcite veins and minor pyrite. Mineralization: 0.35% Zn and 0.18% Pb. »									
		« 139.80- 141.20 Barren siliceous to slightly calcareous mudstone. »									
		« 141.20- 141.50 Siliceous mudstone, very rich in py concretions. Mineralization: 2.1% Zn and 0.8% Pb. »									
		« 141.50- 150.10 Barren siliceous mudstone. »									
		« 150.10- 150.30 Siliceous mudstone containing a 20cm long galena stringer visible on both sides of the core. Mineralization: 0.8% Zn & 6.9% Pb. »									
		« 150.30- 151.90 Barren siliceous mudstone. »									
		« 151.90- 152.30 Siliceous mudstone displaying faint bedding. Mineralization: 1.1% Zn & 0.2% Pb. »									
		< @ 152.00 S0 defined by faint bed S0 tca 71° >									
		« 152.30- 152.40 Barren siliceous mudstone »									
		« 152.40- 152.70 Siliceous to faint calcareous mudstone, rich in pyrite. Mineralization: 1.5% Zn & 0.8% Pb. »									
		« 152.70- 152.90 Broken core of siliceous mudstone. »									
		« 152.90- 153.30 Siliceous mudstone. Mineralization: 1.9% Zn & 0.4% Pb.									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-191

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
»											
« 153.30- 153.50 Barren siliceous mudstone. »											
« 153.50- 154.00 Siliceous mudstone displaying faintly developed bedding. Mineralization: 1.25% Zn & 0.5% Pb. »											
« 154.00- 154.50 Barren calcareous mudstone. »											
« 154.50- 154.70 A breccia of siliceous mudstone, quartz, limestone and pyrite. Mineralization: 0.24% Zn & 1.1% Pb »											
« 154.70- 154.95 Limestone »											
« 154.95- 155.10 Slightly calcareous mudston. Mineralization: 1.7% Zn & 0.6% Pb. »											
« 155.10- 155.30 Limestone »											
« 155.30- 155.80 Barren calcareous/siliceous mudstone. Contains flt gg + flt bx + brco »											
« 155.80- 156.90 Black siliceous mudstone containing a 30mm long Galena concretion. Mineralization: 0.6% Zn & 1.9% Pb. »											
« 156.90- 159.70 Barren siliceous mudstone and limestone rich in quartz veins. Minor pyrite concretions. »											
« 159.70- 160.80 Calcareous mudstone and limestone. Mineralization: 1% Zn & 0.5% Pb. »											
« 160.80- 161.20 Siliceous mudstone displaying faint bedding and bands of pyrite. Mineralization: 0.9% Zn »											
« @ 161.00 S0 defined by faint beds S0 tca 36° »											



Hole Number:
XYC-191

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

Page: 9

Diamond Drill Log

Comprehensive Report for Hole:

XYC-190

Hole No.: XYC-190	Depth: 469.40 m	Horizontal Length: 0.00 m	Project: 1710
Location Data:			
Property:	Selwyn Project	Claim Name:	X 11
Mining District:	Selwyn Basin	Grant Number:	Y64536
Province/Territory:	Yukon		
UTM Co-Ordinates & Altitude of Drill Hole Collar:			
UTM Easting:	488600.96 m	True Azimuth:	15.0 °
UTM Northing:	6926655.21 m	Hole Angle:	-83.0 °
Elevation (m):	1636.21 m	NTS Name:	Placer Creek
		NTS Number:	105I06
Grid Co-Ordinates of Drill Hole Collar:			
Grid Easting (m):	0.00 m	Grid Name:	HP 06
Grid Northing (m):	0.00 m	Grid Type:	100m
Grid Azimuth:	75.0 °		
Dimond Drilling Contract:			
Drilled By:	NL-01	Date Drilling Start:	06/21/2010
		Date Finish:	07/01/2010
Diamond Drill Core:			
Logged By:	Jelle De Bruyckere / Gabe	Date Logging Start:	06/22/2010
		Date Finish:	07/03/2010
Legend for Core Logging Codes: PAX			
Core Size:	NQ3	Cemented:	Yes
Casing Depth:	15.20 m	Casing Pulled:	Yes
Water Depth:	0.00 m	Overburden Depth:	15.20 m
Level:			
Section:		Drift:	

Selwyn Project

Diamond Drill Log

Survey Data for Hole

XYC-190

Hole Comments:

Tue, Jun 22 --- The drillers moved from Don-143 to the current site and set up XYC-190 yesterday. In the past 24 hour, they drilled 77' including 50' casing and did a Flexit Test at 77'.

=====

Wed, Jun 23 --- In the 24 hours, they drilled 200' and did 2 Flexit test. Last night, heavy rain washed out some earth around the rig and also they had some problems with pump and engine alternator. Keith/Dale will deal with them today and move the fly drill as well.

=====

Thu, Jun 24 --- Yesterday morning, at the depth of 285' there was a water loss problem and driller put down superG to seal fractures. In the afternoon, they pulled out rods and added the extension barrel for devico. The drilling was smooth in the night shift with the usage of devico. The depth is at 441' in FLMD and the contact is roughly at 332'.

=====

Fri, Jun 25 --- The depth is at 661' in FLMD at the morning shift. No major problem is reported regarding drilling. Roger, the devicore support technician, is going to check the core today.

=====

Sat, Jun 26 --- The depth is at 851' in black cherty mst of FLMD at the morning shift, but seems like it is close to the contact btw FLMD and USMS.

=====

Sun, Jun 27 --- The depth is at 1031' in USMS and the contact with FLMD is at 833' roughly. From 946' to 949', ACTM is present likely due to folding. The dayshift was not able to use Devico properly and needed more training.

=====

Mon, Jun 28 --- The rock is USMS and the drill is at 1201' this morning.

=====

Tue, Jun 29 --- The depth is at 1341' in barren blk siliceous MST of ACTM and likely close to the footwall rock this morning. ACTM starts from 1197' with whitish grey Zn-Pb MST from 1280' to 1321'.

=====

Wed, Jun 30 --- The drill is at 1441' in LCMS and the contact btw ACTM and LCMS is at 1376'. This drill will be shut down at 1540' (at 469.4m, another 50m into footwall). The driller changed the bit yesterday and the drill was stocked for several times due to current depth. 1 survey was done.

=====

Thu, Jul 01 --- In LCMS, at 1531, We are drilling one more run and cementing the hole from bottom to 1100 feet.

Selwyn Project

Diamond Drill Log

Survey Data for Hole

XYC-190

<i>Depth</i>	<i>Dip</i>	<i>Azimuth</i>
0.00	-83.0	15.0
23.50	-82.9	18.0
47.90	-83.0	21.6
72.20	-82.9	24.5
96.60	-82.6	24.8
119.20	-82.6	25.2
146.60	-82.2	24.0
171.00	-81.7	23.8
192.30	-81.9	27.1
219.50	-81.8	26.5
241.10	-81.6	26.5
265.50	-82.0	27.3
289.70	-81.9	32.9
314.20	-82.2	33.7
338.60	-82.6	39.9
363.00	-83.1	36.9
387.40	-83.1	44.5
411.80	-84.0	39.7
436.20	-84.9	49.3
466.60	-85.4	59.4

Selwyn Project Diamond Drill Log

Hole Number:
XYC-190

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
0.00	15.20	OVBR									
15.20	101.20	BSSM									
<i>BSSM – Backside Siliceous Mudstone</i> <i>Greyish black laminated chert and siliceous mudstone. Randomly-oriented to bedding-parallel bioturbation is common in the bottom of the unit. « lm chrt 75.00-95.00% », « btrb 0.10-2.00cm »</i> <i>Gabe's part of the log:</i> « 15.20- 101.20 Dark grey siliceous mudstone with squiggly calcite+quartz veins. Faint defined beds; laminated pyrite, elongated concretions and squiggly light grey cherty bands with widths of 3mm-10mm; pyrite+calcite+quartz veins are present; locally limestone clasts/nodules are visible with or without graded beds; occasionally interbedded light grey cherty bands and dark mudstone showing USMS texture. » « @ 23.10 S0 defined by faint distorted beds - S0 tca 65° » « @ 37.20 S0 defined by undistorted beds - S0 tca 40° » « @ 51.20 S0 defined by faint distorted beds - S0 tca 80° » « 60.70- 67.50 Flt »« flt gg 10%»« flt bx 30%»« brco 60%» « 67.50- 89.70 More white quartz+calcite veins and veinlets »											
101.20	253.60	FLMD									
<i>FLMD – Flaggy Mudstone Formation</i> <i>Dark grey mudstone in the upper portions of the unit grading into light grey mudstone to siltstone. Contains abundant wispy bioturbation which ranges from randomly-oriented at the top of the unit to bedding-parallel throughout the majority of the unit. Darker upper section has a strong fetid odour along</i>											

Selwyn Project Diamond Drill Log

Hole Number:
XYC-190

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
broken surfaces. « btrb 0.10-2.00cm », « cg xtl crns ca 1.00-5.00% 5.00-150.00cm », « crns py 1.00-5.00% 0.10-0.50mm » « 101.20- 253.60 Light grey bioturbated siliceous mudstone, interbedded locally with dark grey siliceous non-carbonaceous mudstone. Pyrite+calcite+quartz nodules are present. Bedding varies from 10 to 60 degrees tca. » < @ 103.40 S0 defined by black slightly bioturbated bands - S0 tca 40° > < @ 116.90 S0 defined by black laminated stretches - S0 tca 45° > < @ 129.30 S0 defined by black laminated stretches - S0 tca 40° > < @ 143.20 S0 defined by black laminated stretches - S0 tca 35° > « 134.40- 147.80 Light grey silty siliceous mudstone » « 169.60- 185.00 Black siliceous slightly carbonaceous mudstone without apparent bedding, pyrite nodules, calcareous clasts and calcite veins. » < @ 185.70 S0 defined by black bands - S0 tca 53° >											
253.60	333.60	USMS	631601	287.30	287.80	0.50	0.08	0.11	1.00	5.00	0.73
USMS – Upper Siliceous Mudstone			631602	287.80	288.70	0.90	0.03	0.08	1.00	5.00	0.38
Consists of interlaminated dark grey to black mudstone and light to medium grey chert. Regionally, a 1m thick graptolite zone occurs 15m below the top of the upper unit, this is usable as a horizon. The USMS is divided into 3 units. The Lower Unit contains abundant limestone concretions and Galena and sphalerite micro-concretions occur locally near the base of this unit. « gra , lm chrt -20.00% », « cg xtl sph crns ca 5.00-20.00cm », « bed chrt 10.00-15.00% » « 253.60- 333.60 Dark grey siliceous mudstone with medium grey cherty bands. »			631603	288.70	289.20	0.50	0.43	7.16	6.00	180.00	0.06
			631604	289.20	289.60	0.40	0.08	0.09	1.00	5.00	0.89
			631605	289.60	289.90	0.30	0.03	0.02	1.00	5.00	1.50
			631606	323.50	323.60	0.10	0.19	0.69	1.00	20.00	0.28
			631607	333.10	333.60	0.50	0.01	0.10	1.00	5.00	0.10

Selwyn Project Diamond Drill Log

Hole Number:
XYC-190

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		« 253.60- 263.00 Dark grey siliceous mudstone with faint pyrite defined beds; locally disseminated fine calcite grains are present. » ◁ @ 253.90 S0 defined by faintly defined pyrite beds - S0 tca 43° ▷ ◁ @ 267.30 S0 defined by faintly defined pyrite beds - S0 tca 52° ▷ ◁ @ 276.60 S0 defined by faintly defined pyrite beds - S0 tca 37° ▷ ◁ @ 293.80 S0 defined by faintly defined pyrite beds - S0 tca 30° ▷ « 288.20- 288.40 Flt »« flt gg 30%» « 288.40- 288.70 Broken calcite + quartz vein » « 288.70- 289.20 Mineralized section within USMS » « 289.00- 344.70 S0 tca changes from 80degrees to 30degrees. Lst nodules/concretions and squiggly calcite+quartz veins are present ubiquitous. » « 314.90- 315.60 flt »« flt gg 10%»« flt bx and brco 90% » Jelle's part of the log begins here: ◁ @ 293.70 S0 tca 50° ▷ ◁ @ 293.70 Beta 309° ▷ « 329.10- 329.70 Typical coarse carbonate concretion for USMS, displaying a twinning effect. » « 330.80- 331.80 Coarse carbonate concretion » « 331.80- 333.60 Siliceous mudstone with chert bands, squiggly carbonate bands and thin elongated pyrite concretions. »									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-190

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
333.60	419.30	ACTM									
<i>ACTM – Active Member</i>			631608	333.60	334.10	0.50	0.01	0.24	1.00	5.00	0.04
<i>The ACTM consists of a repetitive, possibly rhythmic, sequence of intercalated carbonaceous mudstone, cherty mudstone, chert and limestone and locally contains economically significant Zn and Pb sulphides (see bold marked facies), mainly in its sections with well developed lamination. Because of its heterogeneity, the member is distinctive and easily identified.</i> ===== <i>The ACTM has 8 different facies:</i> ===== - GREY CHERT FACIES: <i>Consists of laminated medium light grey to medium dark grey chert. Mineralization: 95-99% quartz and up to 5% secondary calcite.</i> - WHITISH GREY ZN-PB MUDSTONE FACIES: <i>Is a laminated cherty rock containing up to 70% sulphides. Mineralization: quartz, sphalerite and galena are the major minerals with only minor amounts of pyrite and locally calcite. Sedimentary diagenetic structures are common and well displayed in the facies, such as: lamination, pseudo-beds, calcite nodules & limestone nodules and abundant water escape structures. Most obvious structure in facies is cross-cutting veins containing massive sphalerite and galena with minor pyrite. They range in width from 0.5 to 10mm.</i> - THIN BEDDED CHERTY MUDSTONE FACIES: <i>Consists of rhythmic intercalated laminae of chert, carbonaceous mudstone and minor micrite. This facies contains significant amounts of Zn and Pb sulphides.</i> - CHERTY MUDSTONE FACIES: <i>Consists of a greyish black monotonous siliceous, carbonaceous mudstone. It is most typically found overlying the thin bedded calcareous mudstone facies.</i>			631609	334.10	334.50	0.40	0.01	0.02	1.00	5.00	0.50
			631610	334.50	334.80	0.30	0.01	0.26	1.00	5.00	0.04
			631611	334.50	334.80	0.30	0.01	0.42	1.00	5.00	0.02
			631612	334.80	335.60	0.80	0.01	0.04	1.00	5.00	0.25
			631613	335.60	336.10	0.50	0.01	0.05	1.00	5.00	0.20
			631614	336.10	336.80	0.70	0.01	0.12	1.00	5.00	0.08
			631615	336.80	337.10	0.30	0.01	1.04	1.00	20.00	0.01
			631616	337.10	337.30	0.20	0.01	0.10	1.00	5.00	0.10
			631617	337.30	338.40	1.10	0.01	0.03	1.00	5.00	0.33
			631618	338.40	339.70	1.30	0.01	0.18	1.00	5.00	0.06
			631619	339.70	340.20	0.50	0.01	0.18	1.00	5.00	0.06
			631620	340.20	340.20	0.00	0.01	0.01	1.00	5.00	2.00
			631621	340.20	340.80	0.60	0.01	0.29	1.00	5.00	0.03
			631622	340.80	341.30	0.50	0.01	0.17	1.00	5.00	0.06
			631623	341.30	341.50	0.20	0.01	0.12	1.00	5.00	0.08
			631624	341.50	342.00	0.50	0.01	0.18	1.00	5.00	0.06
			631625	342.00	342.50	0.50	0.25	0.50	3.00	10.00	0.50
			631626	342.50	343.40	0.90	0.01	0.21	1.00	5.00	0.05
			631627	343.40	344.70	1.30	0.01	0.01	1.00	5.00	2.00
			631628	344.70	345.90	1.20	0.03	0.01	1.00	5.00	6.00
			631629	345.90	346.20	0.30	0.20	1.41	2.00	40.00	0.14
			631630	346.20	346.20	0.00	5.87	6.68	69.00	180.00	0.88
			631631	346.20	346.40	0.20	0.01	3.00	1.00	90.00	0.00
			631632	346.40	346.70	0.30	0.02	2.02	1.00	60.00	0.01
			631633	346.70	347.80	1.10	0.01	0.01	1.00	5.00	2.00
			631634	347.80	348.30	0.50	0.79	0.01	2.00	5.00	158.0
			631635	348.30	348.50	0.20	0.44	1.68	4.00	50.00	0.26
			631636	348.50	349.50	1.00	0.03	0.40	1.00	10.00	0.08
			631637	349.50	349.60	0.10	0.01	0.35	1.00	10.00	0.03
			631638	349.60	350.90	1.30	0.01	0.13	1.00	5.00	0.08
			631639	350.90	351.10	0.20	0.01	0.77	2.00	30.00	0.01
			631640	351.10	351.60	0.50	0.01	0.65	4.00	20.00	0.02

Selwyn Project Diamond Drill Log

Hole Number:
XYC-190

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
- THIN BEDDED CALCAREOUS MUDSTONE FACIES: Consists of laminated carbonaceous mudstone containing 20-40% calcite, 40-55% quartz and 10-20% muscovite. Sulphides occur in laminae. In the XY area it is usually the lowest facies in the section to contain laminated sulphides. - CALCAREOUS MUDSTONE FACIES: Consists of grey to greyish black monotonous, calcareous siliceous carbonaceous mudstone. There are no feathery calcite beds or pyrite-calcite blebs in the facies, making it easily distinguishable from the CCMS. - GRADED LIMESTONE FACIES: Is a laminated argillaceous limestone with intercalated carbonaceous limestone laminae. The main rock type in the facies is laminated limestone with laminae up to 0.1-7mm thick. - LIGHT GREY BASAL LIMESTONE FACIES - LGLS: Consists of laminated argillaceous limestone. In the Anniv area it marks the end of the ACTM. It's not always present in the stratigraphy. - BASAL FACIES: This is a highly contorted and locally foliated carbonaceous mudstone. Unlike the other facies it is not repeated higher in the member. It appears locally to contain the slip zone of a major slump. The facies has only been observed in the YX area. It is 0.1-2m thick. The facies consists of massive carbonaceous siliceous mudstone with lenses and laminae of contorted, slightly carbonaceous chert. « 333.60- 337.30 Siliceous mudstone with 3 visible limestone concretions (2mm to 7cm diameter). Chert bands are present. It looks like USMS, but very low Zn mineralization is present. Pyrite concretions are present. » « 337.30- 338.40 Coarse carbonate concretion » « 338.40- 341.30 Siliceous mudstone with chert bands. Low Zn			631641	351.10	351.60	0.50	0.01	0.59	4.00	20.00	0.02
			631642	351.60	352.80	1.20	0.01	0.17	2.00	5.00	0.06
			631643	352.80	353.40	0.60	0.01	0.16	1.00	5.00	0.06
			631644	353.40	353.90	0.50	0.01	0.05	1.00	5.00	0.20
			631645	353.90	354.30	0.40	0.01	0.26	2.00	5.00	0.04
			631646	354.30	355.60	1.30	0.01	0.12	1.00	5.00	0.08
			631647	355.60	355.90	0.30	0.01	0.13	1.00	5.00	0.08
			631648	355.90	356.30	0.40	0.01	0.11	1.00	5.00	0.09
			631649	356.30	356.60	0.30	0.37	0.52	3.00	20.00	0.71
			631650	356.60	356.60	0.00	0.01	0.01	1.00	5.00	2.00
			631551	356.60	357.80	1.20	0.04	0.17	1.00	5.00	0.24
			631552	357.80	358.80	1.00	0.01	0.16	1.00	5.00	0.06
			631553	358.80	359.40	0.60	0.52	0.08	1.00	5.00	6.50
			631554	359.40	360.00	0.60	0.01	0.26	1.00	5.00	0.04
			631555	360.00	361.20	1.20	0.01	0.19	1.00	5.00	0.05
			631556	361.20	361.70	0.50	1.20	0.02	1.00	5.00	60.00
			631557	361.70	362.50	0.80	0.01	0.13	1.00	5.00	0.08
			631558	362.50	363.40	0.90	0.01	0.32	1.00	10.00	0.03
			631559	363.40	363.70	0.30	0.04	0.63	3.00	30.00	0.06
			631560	363.70	363.70	0.00	1.47	2.98	19.00	180.00	0.49
			631561	363.70	364.20	0.50	0.03	0.35	1.00	20.00	0.09
			631562	364.20	365.40	1.20	0.22	0.42	1.00	20.00	0.52
			631563	365.40	366.90	1.50	0.12	0.89	2.00	50.00	0.13
			631564	366.90	367.30	0.40	3.56	7.10	6.00	350.00	0.50
			631565	367.30	368.00	0.70	0.76	3.03	2.00	150.00	0.25
			631566	368.00	369.10	1.10	0.99	3.23	1.00	180.00	0.31
			631567	369.10	370.40	1.30	0.69	2.18	1.00	120.00	0.32
			631568	370.40	371.90	1.50	1.17	2.21	1.00	80.00	0.53
			631569	371.90	373.40	1.50	3.08	7.28	4.00	260.00	0.42
			631570	373.40	374.60	1.20	1.16	9.41	5.00	320.00	0.12
			631571	373.40	374.60	1.20	2.32	9.82	4.00	340.00	0.24
			631572	374.60	375.60	1.00	0.94	5.72	3.00	160.00	0.16
			631573	375.60	376.50	0.90	1.38	6.34	1.00	160.00	0.22

Selwyn Project Diamond Drill Log

Hole Number:
XYC-190

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
mineralization. »			631574	376.50	377.30	0.80	0.94	2.11	1.00	60.00	0.45
« 341.30- 341.50 Limestone »			631575	377.30	378.10	0.80	0.05	0.49	1.00	10.00	0.10
« 341.50- 343.40 Siliceous mudstone rich in quartz veining. Low Zn mineralization. Carbonate and chert bands present. »			631576	378.10	378.90	0.80	0.03	0.63	1.00	20.00	0.05
« 343.40- 346.00 Very calcareous mudstone, light grey to dark grey. »			631577	378.90	380.00	1.10	0.07	0.50	1.00	20.00	0.14
« 346.00- 346.70 Siliceous mudstone with 1% Zn & 1% Pb. One 15cm section of 4% Zn. »			631578	380.00	381.30	1.30	0.03	0.30	1.00	5.00	0.10
« 346.70- 347.80 Limestone »			631579	381.30	382.10	0.80	3.90	12.48	1.00	330.00	0.31
« 347.80- 348.30 Calcareous mudstone »			631580	382.10	382.10	0.00	0.01	0.01	1.00	5.00	1.00
« 348.30- 356.30 Siliceous mudstone with Zn & Pb mineralization and some chert bands. < @ 354.00 SO tca 68° > @ 354.00 Beta 68° >			631581	382.10	383.20	1.10	2.19	12.01	3.00	330.00	0.18
« 356.30- 356.60 Black siliceous mudstone with visible Galena. Pb & Zn mineralization »			631582	383.20	384.60	1.40	0.05	0.47	1.00	10.00	0.11
« 356.60- 361.20 Siliceous mudstone with chert bands, minor limestone concretions, calcite veining, visible Galena »			631583	384.60	385.70	1.10	1.20	5.67	1.00	150.00	0.21
« 361.20- 361.70 Coarse carbonate concretion, upper half is rich in pyrite, with even visible Galena. It shows moderately developed parallel banding and minor twinning effect. »			631584	385.70	386.60	0.90	0.66	3.89	1.00	100.00	0.17
« 361.70- 366.90 Siliceous mudstone with visible Galena. Two 40cm long sections with 0.5% Zn. »			631585	386.60	387.90	1.30	1.08	4.18	1.00	120.00	0.26
« 366.90- 367.30 Siliceous mudstone with visible Galena and Sphalerite. Calcite veins and pyrite present. »			631586	387.90	388.70	0.80	0.84	3.92	1.00	100.00	0.21
			631587	388.70	389.50	0.80	1.47	7.90	2.00	230.00	0.19
			631588	389.50	390.20	0.70	2.38	9.01	2.00	300.00	0.26
			631589	390.20	391.50	1.30	7.99	22.67	5.00	830.00	0.35
			631590	391.50	391.50	0.00	5.97	6.78	71.00	180.00	0.88
			631591	391.50	392.00	0.50	1.08	3.85	1.00	110.00	0.28
			631592	392.00	392.30	0.30	0.47	0.42	1.00	20.00	1.12
			631593	392.30	392.70	0.40	9.56	7.63	3.00	420.00	1.25
			631594	392.70	392.90	0.20	8.37	1.52	3.00	80.00	5.51
			631595	392.90	393.50	0.60	11.90	18.45	4.00	860.00	0.64
			631596	393.50	394.10	0.60	9.98	16.62	3.00	770.00	0.60
			631597	394.10	394.70	0.60	7.06	10.33	1.00	450.00	0.68
			631598	394.70	395.20	0.50	6.67	12.06	1.00	550.00	0.55
			631599	395.20	395.80	0.60	7.77	13.12	1.00	620.00	0.59
			631600	395.80	396.40	0.60	12.64	20.85	1.00	1030.00	0.61
			632101	395.80	396.40	0.60	13.01	21.61	2.00	1070.00	0.60
			632102	396.40	397.20	0.80	7.31	13.92	1.00	660.00	0.53
			632103	397.20	397.70	0.50	5.03	15.85	3.00	540.00	0.32
			632104	397.70	398.10	0.40	17.44	20.28	9.00	980.00	0.86
			632105	398.10	398.60	0.50	14.40	19.92	7.00	950.00	0.72
			632106	398.60	399.10	0.50	14.95	16.94	6.00	920.00	0.88
			632107	399.10	399.70	0.60	15.80	18.84	8.00	1010.00	0.84
			632108	399.70	400.00	0.30	13.49	18.36	12.00	1030.00	0.73

Selwyn Project Diamond Drill Log

Hole Number:
XYC-190

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
« 367.30- 368.00 Calcareous mudstone very rich in pyrite and calcite. » « 368.00- 371.90 Limestone very rich in calcite veining » « 371.90- 376.50 Siliceous mudstone with well developed lamination. Sphalerite and Galena present. Pyrite and some limestone clasts present (1-12cm diameter). » « 376.50- 378.10 Laminated calcareous mudstone with visible Galena. Limestone present. Calcite veining. Minor pyrite present. Sphalerite and Galena mineralization. » « 378.10- 378.90 Laminated siliceous mudstone with Sphalerite and Galena mineralization » < @ 377.80 S0 tca 53° > < @ 378.50 S0 tca 58° > « 378.90- 381.30 Black siliceous mudstone, non mineralized. Squiggly quartz/calcite veins. Pyrite present. » « 381.30- 383.20 Siliceous mineralized mudstone with well developed lamination. Rich in Sphalerite and Galena. » « 384.60- 385.70 Siliceous mineralized mudstone with well developed lamination. Sphalerite and Galena are present, but not as rich as the previous section. » « 385.70- 387.90 Calcareous mudstone with visible Galena and Sphalerite. Thin Bedded Calcareous Mudstone Facies » « 387.90- 389.50 Siliceous mudstone with well developed lamination. Visible Sphalerite crystals. Sphalerite + Galena mineralization. »			632109	400.00	400.60	0.60	16.14	19.37	9.00	1060.00	0.83
			632110	400.60	400.60	0.00	0.05	0.05	1.00	5.00	1.00
			632111	400.60	401.10	0.50	17.74	19.36	10.00	990.00	0.92
			632112	401.10	401.70	0.60	9.89	25.77	6.00	1130.00	0.38
			632113	401.70	402.30	0.60	4.22	19.02	5.00	530.00	0.22
			632114	402.30	402.50	0.20	4.47	26.57	5.00	660.00	0.17
			632115	402.50	402.70	0.20	3.62	27.37	10.00	740.00	0.13
			632116	402.70	403.70	1.00	0.20	0.12	1.00	5.00	1.67
			632117	403.70	404.60	0.90	0.22	0.60	1.00	30.00	0.37
			632118	404.60	405.70	1.10	4.36	3.63	4.00	170.00	1.20
			632119	405.70	407.10	1.40	0.07	0.62	1.00	20.00	0.11
			632120	407.10	407.10	0.00	1.45	2.99	17.00	180.00	0.48
			632121	407.10	408.20	1.10	0.18	0.46	1.00	20.00	0.39
			632122	408.20	409.20	1.00	0.01	0.03	1.00	5.00	0.33
			632123	409.20	410.00	0.80	0.21	0.23	2.00	5.00	0.91
			632124	410.00	410.80	0.80	0.41	1.91	6.00	70.00	0.21
			632125	410.80	411.80	1.00	0.09	0.53	1.00	20.00	0.17
			632126	411.80	412.90	1.10	0.01	0.21	1.00	5.00	0.05
			632127	412.90	414.00	1.10	0.15	0.42	2.00	10.00	0.36
			632128	414.00	415.10	1.10	0.07	0.82	3.00	30.00	0.09
			632129	415.10	416.30	1.20	0.24	0.92	3.00	40.00	0.26
			632130	416.30	417.00	0.70	0.18	0.18	4.00	5.00	1.00
			632131	416.30	417.00	0.70	0.16	0.18	3.00	5.00	0.89
			632132	417.00	417.90	0.90	0.01	0.01	1.00	5.00	2.00
			632133	417.90	419.30	1.40	0.01	0.01	1.00	5.00	2.00

Selwyn Project Diamond Drill Log

Hole Number:
XYC-190

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6



From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		« 389.50- 390.20 Calcareous mudstone with moderately developed lamination. Visible Sphalerite crystals. Sphalerite and Galena mineralized. » « 390.20- 391.50 Whitish Grey Zn Pb Mudstone Facies. High Grade. » « 391.50- 392.00 Calcareous mudstone with a well developed lamination. Visible Sphalerite and Galena. » « 392.00- 392.30 Calcareous Mudstone Facies. Black monotonous calcareous carbonaceous mudstone. » « 392.30- 392.70 Whitish Grey Zn-Pb Mudstone Facies. High grade ore. » « 392.70- 392.90 Calcareous mudstone with a faint bedding defined by pyrite bands. » « 392.90- 402.50 Whitish Grey Zn-Pn Mudstone Facies. High grade ore. Massive sulphides. » « 402.50- 402.70 Laminated calcareous mudstone. Sphalerite and Galena present. » « 402.70- 404.60 Calcareous mudstone. No laminations. No visible Sphalerite or Galena. » « 404.60- 405.70 Calcareous mudstone with a weakly developed lamination. Sphalerite present. » « 405.70- 407.10 Siliceous mudstone with moderately developed lamination. No significant mineralization. » ◁ @ 405.90 S0 tca 43 ▷ @ 405.90 Beta 275° ▷									

Selwyn Project Diamond Drill Log

Hole Number:
XYC-190

Selwyn Chihong Mining Ltd.
#700-509 Richards Street
Vancouver, British Columbia
Canada, V6B 2Z6

From (m)	To (m)	Rocktype & Description	Sample ID	From (m)	To (m)	Width (m)	Pb (%)	Zn (%)	Ag (ppm)	Cd (ppm)	Pb% / Zn%
		« 407.10- 408.20 Calcareous mudstone with poorly developed lamination. No significant mineralization. »									
		« 408.20- 409.20 Argillaceous limestone displaying some poorly developed bedding. »									
		« 409.20- 415.10 Calcareous mudstone with no obvious bedding. No mineralization. »									
		« 415.10- 417.00 Carbonaceous siliceous mudstone with minor carbonate bands. »									
		« 417.00- 419.30 Basal Light Grey Limestone »									
419.30	469.40	CCMS CCMS – Calcareous Mudstone									
		Massive, calcareous, carbonaceous, dark grey mudstone. Most of the member is massive, but rare poorly defined bedding and pyrite-calcite micro-concretions are present. Most diagnostic structures are feathery calcite beds (=thin calcite-cemented concretions, many of them contain pyrite cores) and calcite pseudo-beds (= fibrous calcite vein parallel to bedding).									
		« lm ca 5.00-10.00mm », « nodules py -3.00% 2.00-20.00mm »									
		« 442.90- 453.10 Fault »« Flt gg 10%»« flt bx 10%»« brco 60%»									
		< @ 459.00 S0 tca 59° >									
469.40	469.40	EOH									

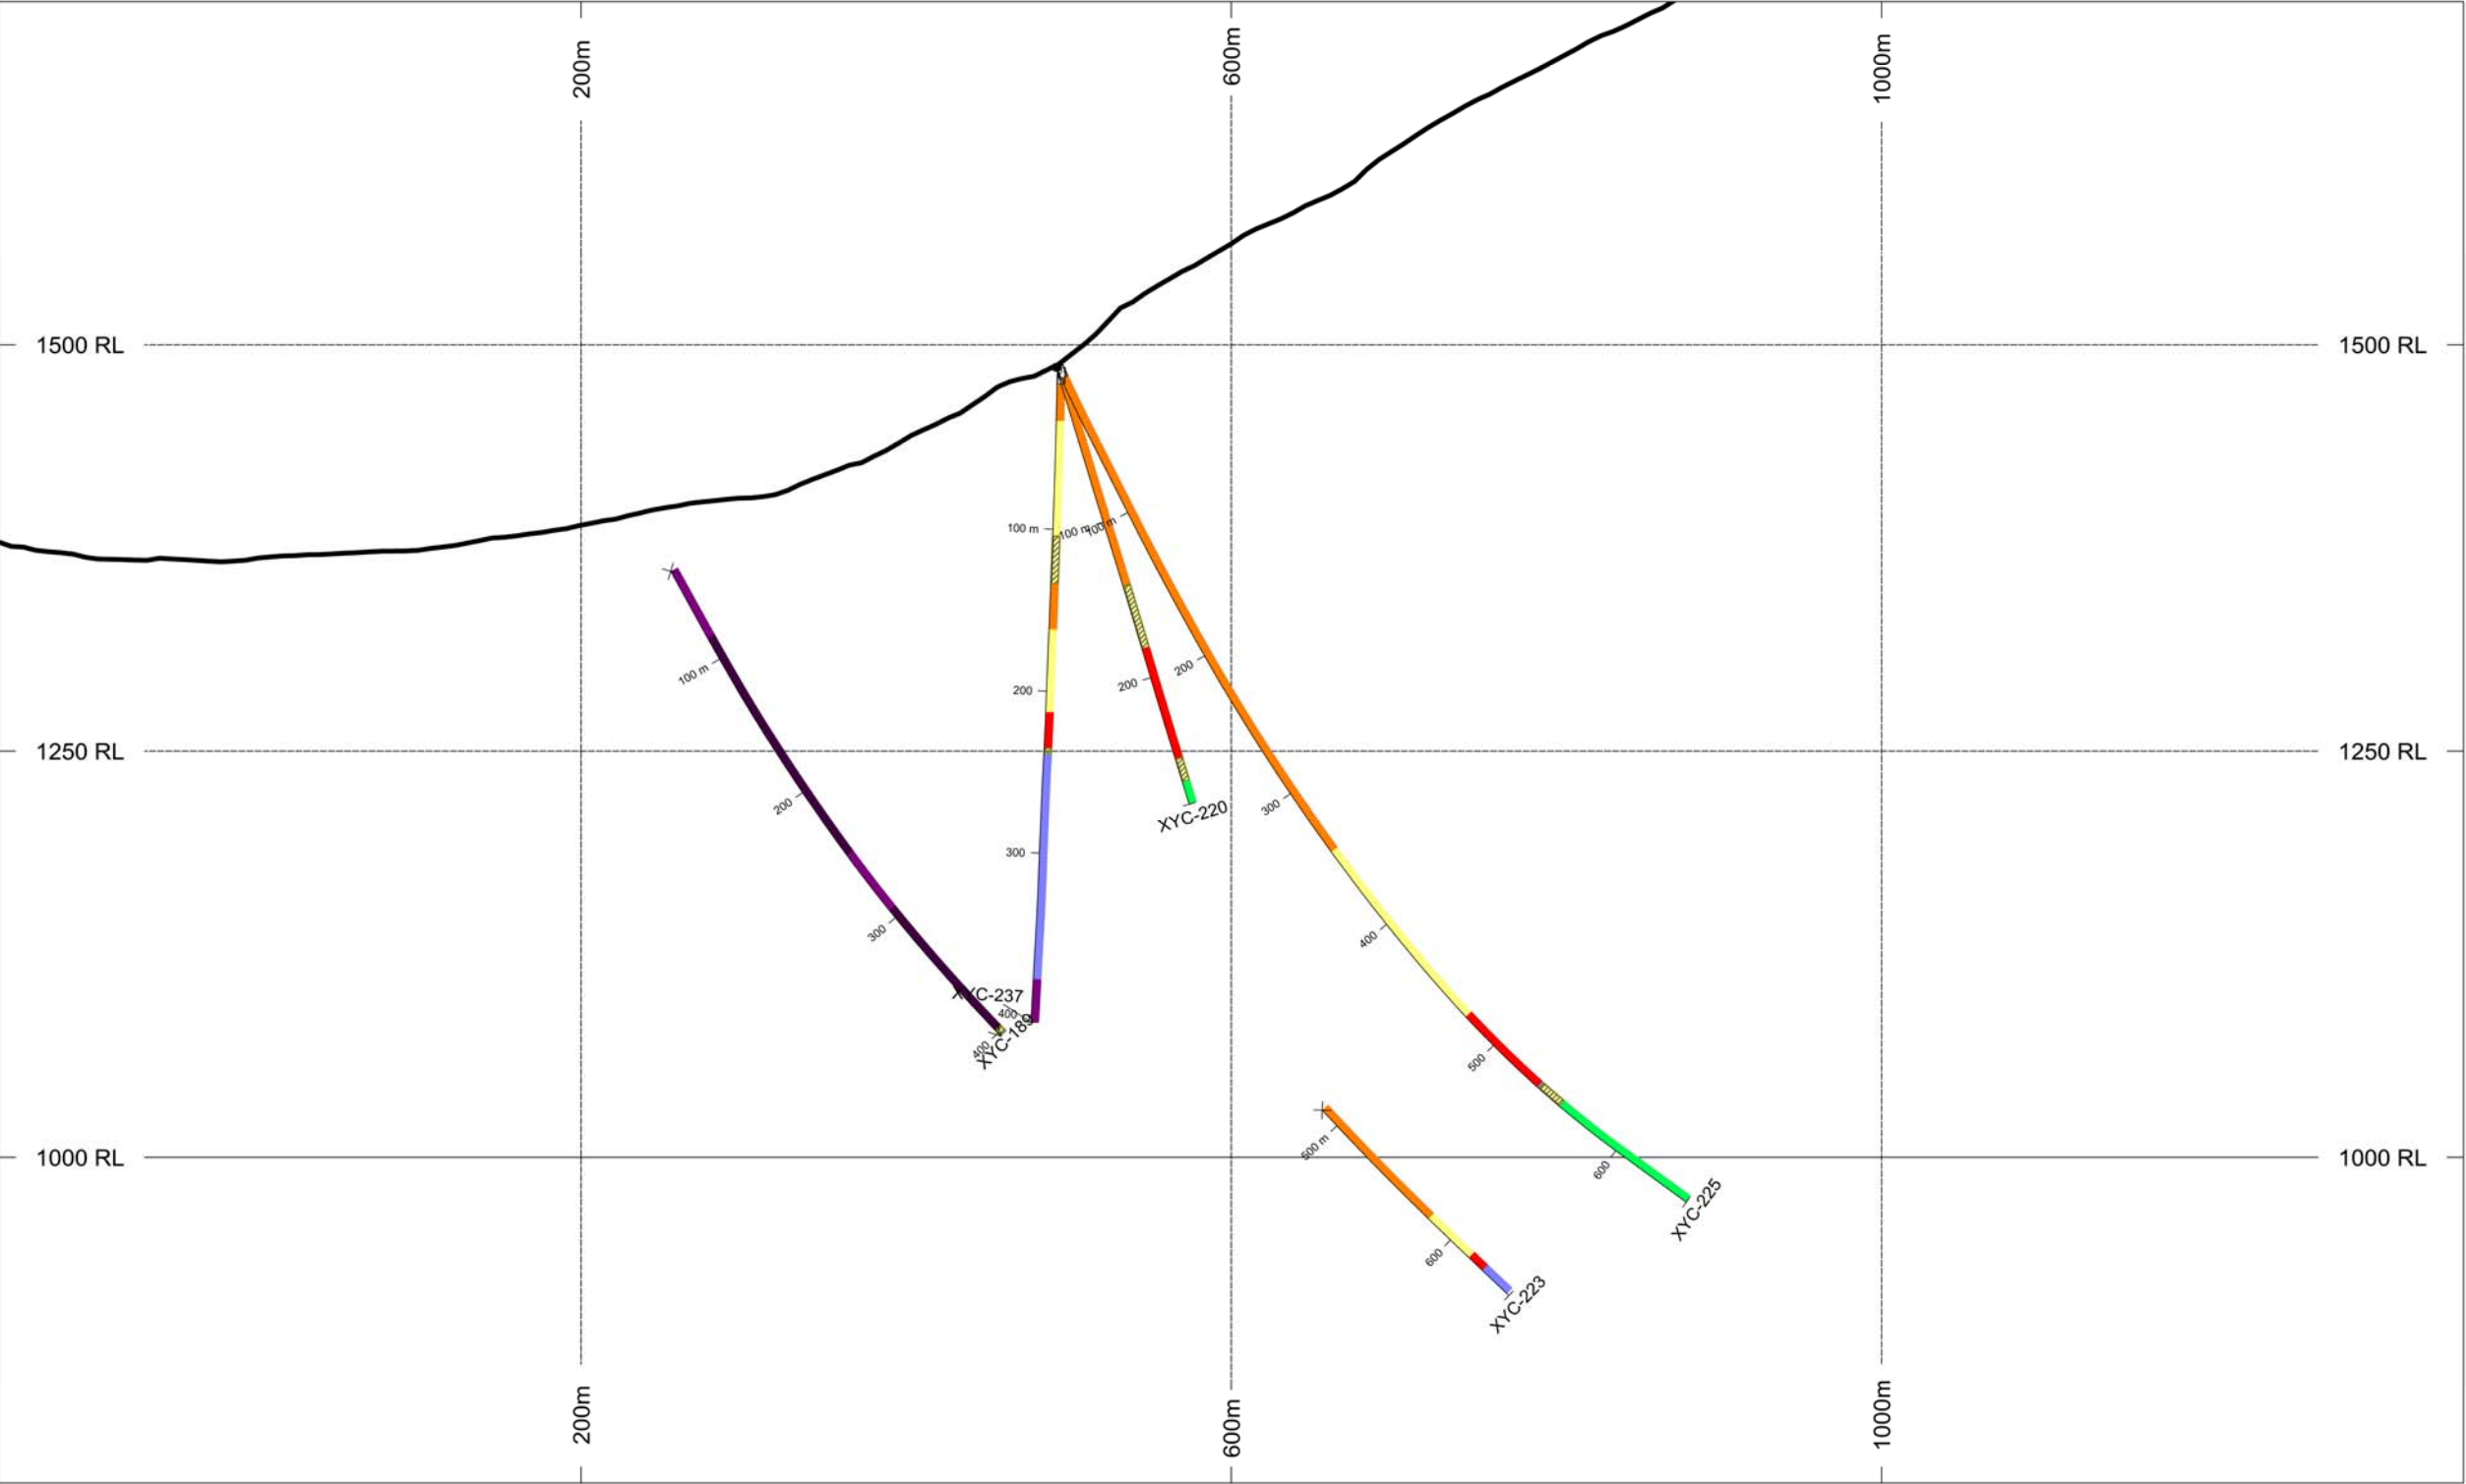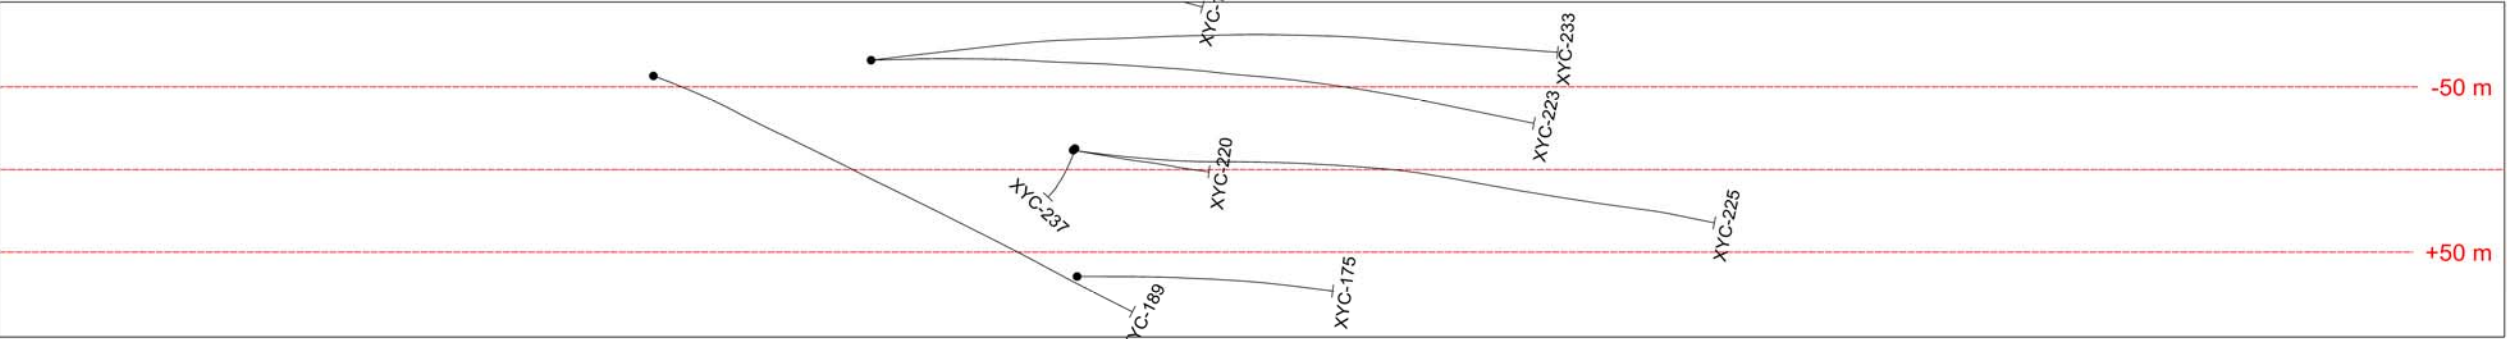

HOLES PLOTTED

TOTAL 5

XYC-189
XYC-237

XYC-220

XYC-223

XYC-225




ROCK CODES	PAT	LABEL	DESCRIPTION
rocktype		OVBR	Overburden
		BSSM	Backside Siliceous Mudstone
		FLMD	Flaggy Mudstone
		USMS	Upper Siliceous Mudstone
		ACTM	Active Member
		CCMS	Calcareous Mudstone
		PSMS	Pyritic Mudstone
		TRAN	Transition Formation
		CLST	Cambrian Limestone
		FLT	Fault

SECTION SPECS:

REF. PT. E, N	487567 m	6927328 m
EXTENTS	1516 m	911.9 m
SECTION TOP, BOT	1711 m	799.3 m
TOLERANCE +/-	50 m	

SCALE 1 : 5000





NAD83 / UTM zone 9N

Selwyn Chihong Mining Ltd.

Selwyn Project, YT

Section L_04200N/0600E

XY West Deposit

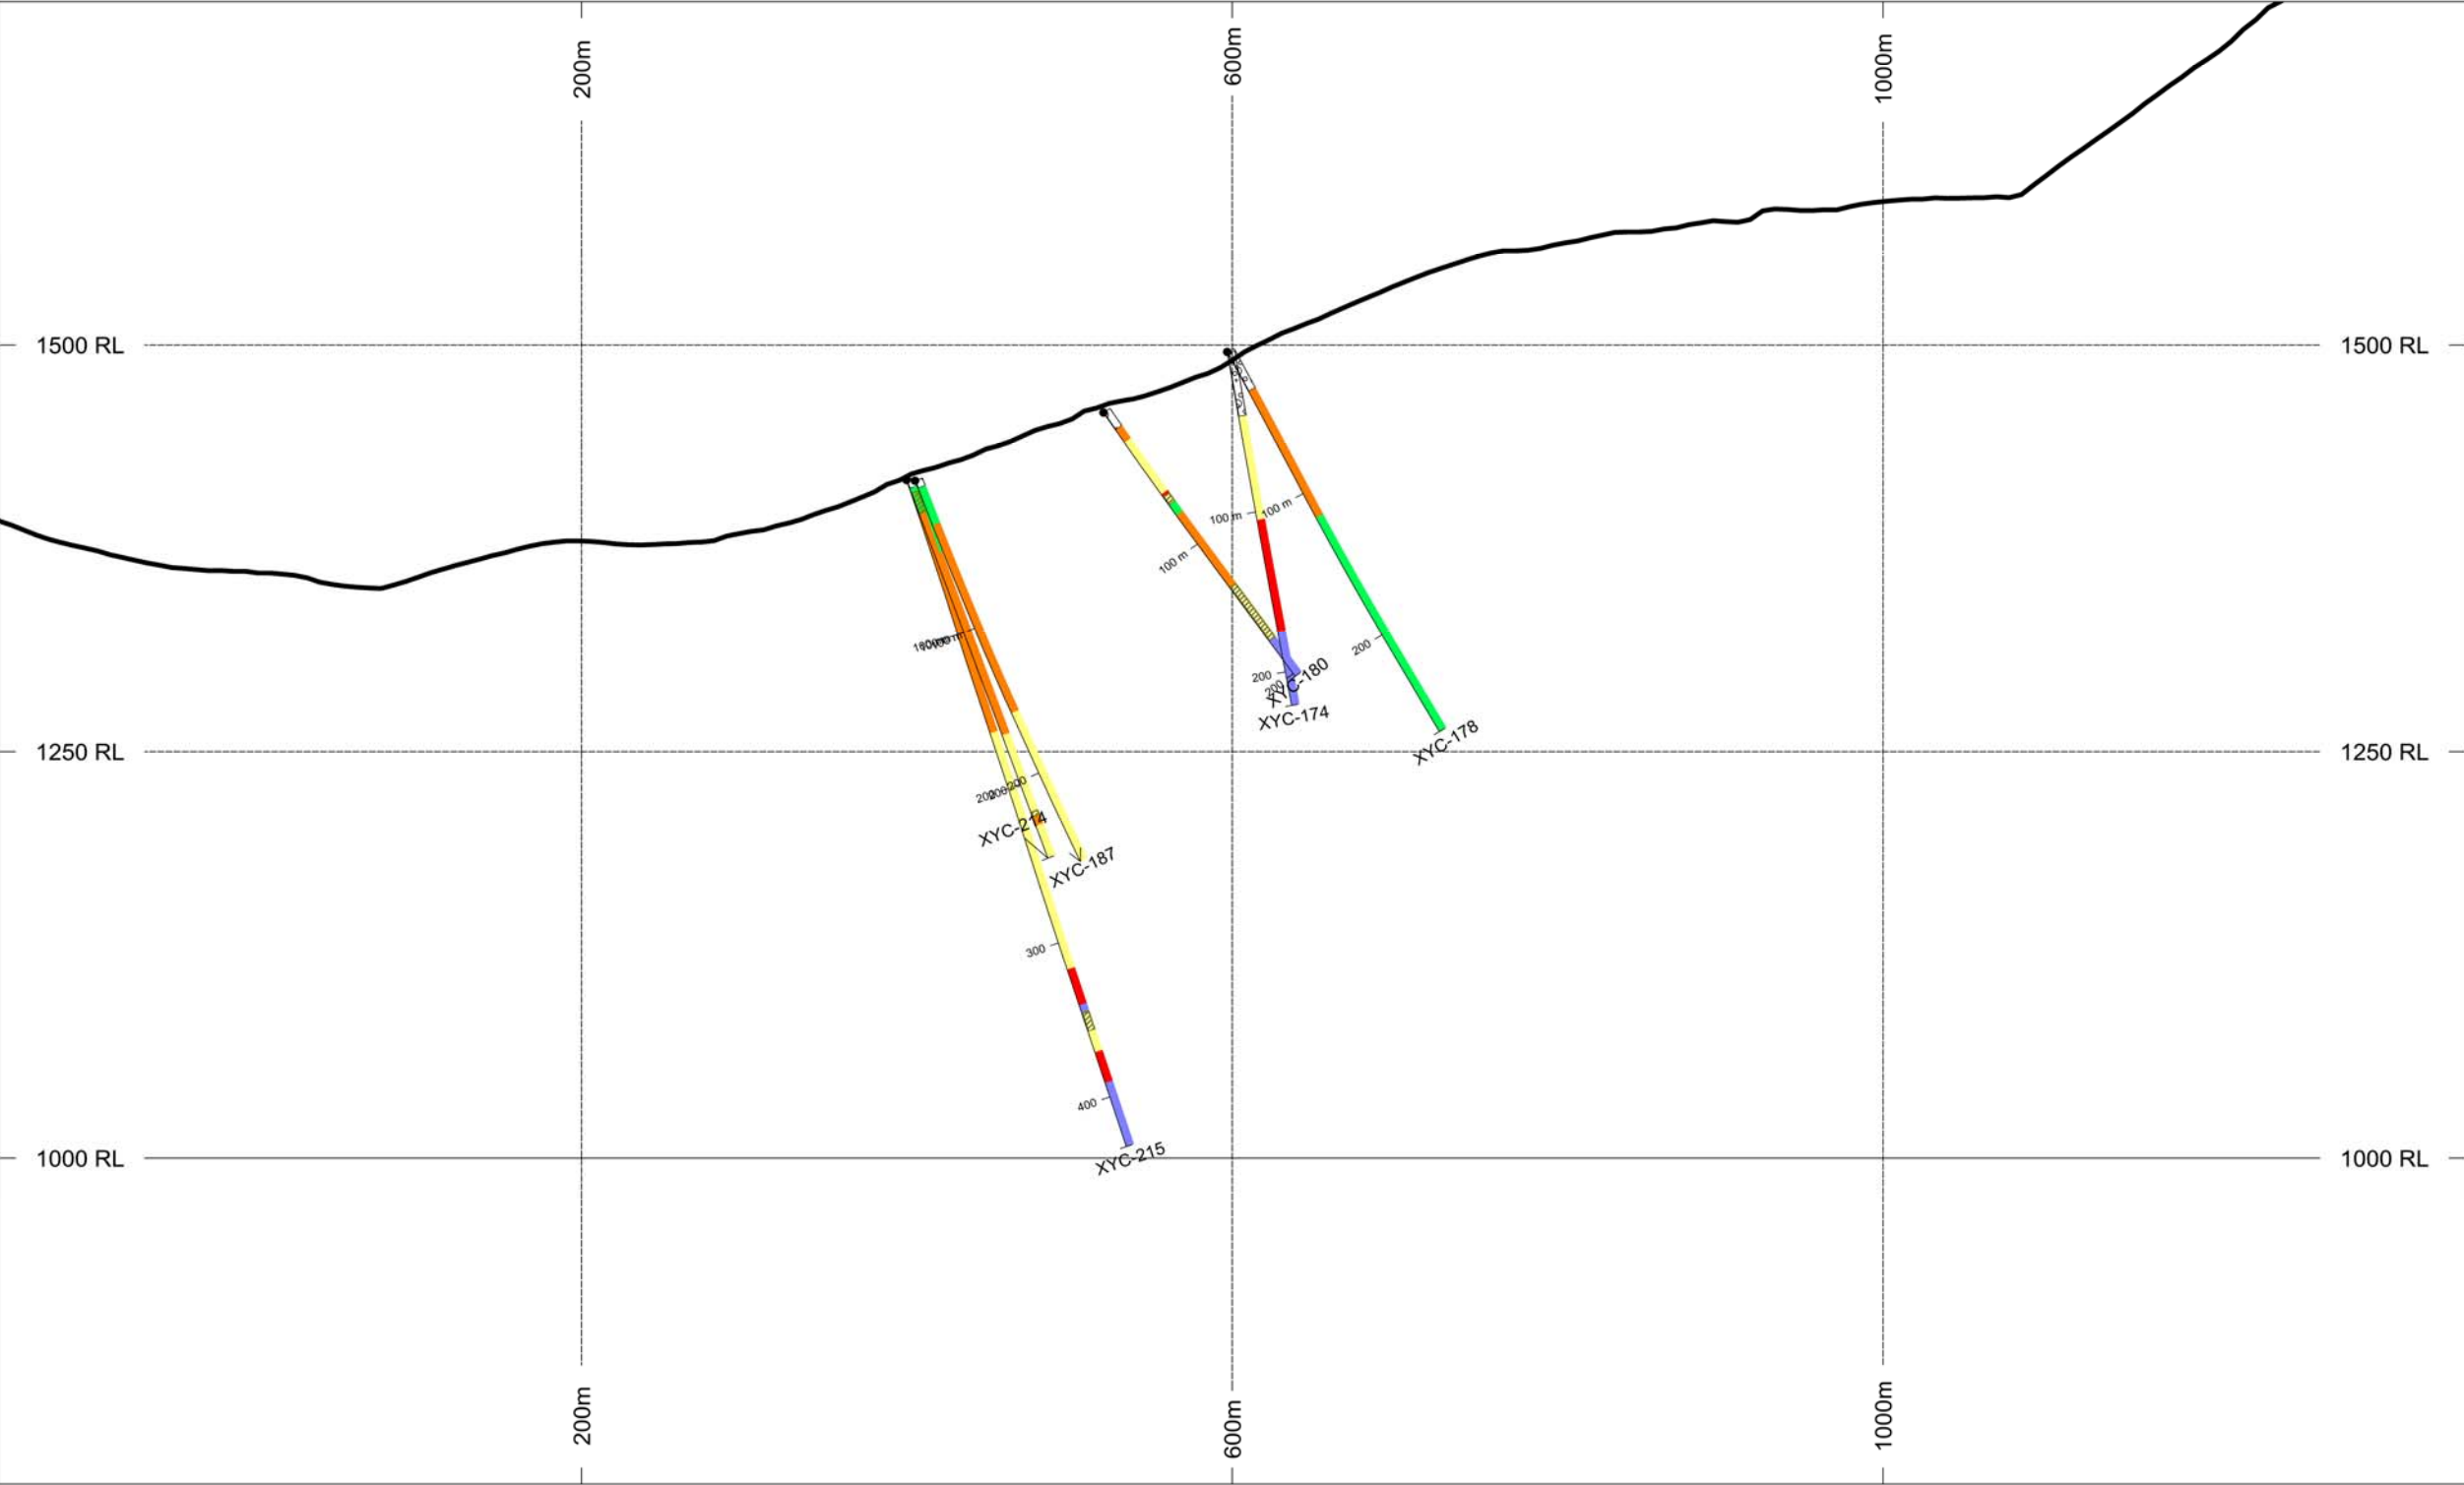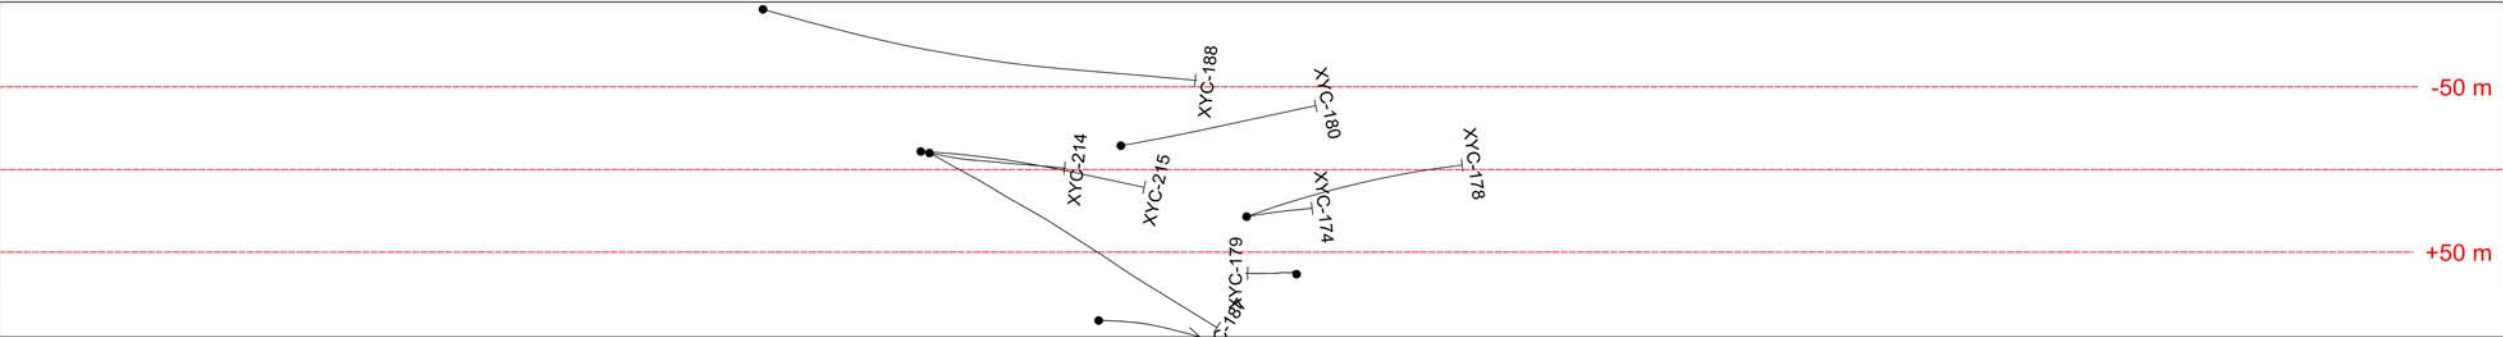

HOLES PLOTTED

TOTAL 6


XYC-174	XYC-178	XYC-180	XYC-187
XYC-214	XYC-215		





ROCK CODES	PAT	LABEL	DESCRIPTION
rocktype		OVBR	Overburden
		BSSM	Backside Siliceous Mudstone
		FLMD	Flaggy Mudstone
		USMS	Upper Siliceous Mudstone
		ACTM	Active Member
		LCMS	Lower Cherty Mudstone
		CCMS	Calcareous Mudstone
		PSMS	Pyritic Mudstone
		TRAN	Transition Formation
		CLST	Cambrian Limestone
		FLT	Fault

SECTION SPECS:

REF. PT. E, N	487394 m	6927428 m
EXTENTS	1516 m	911.9 m
SECTION TOP, BOT	1711 m	799.3 m
TOLERANCE +/-	50 m	

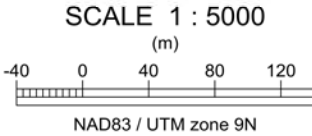

Selwyn Chihong Mining Ltd.
Selwyn Project, YT
Section L_04000N/0600E
XY West Deposit

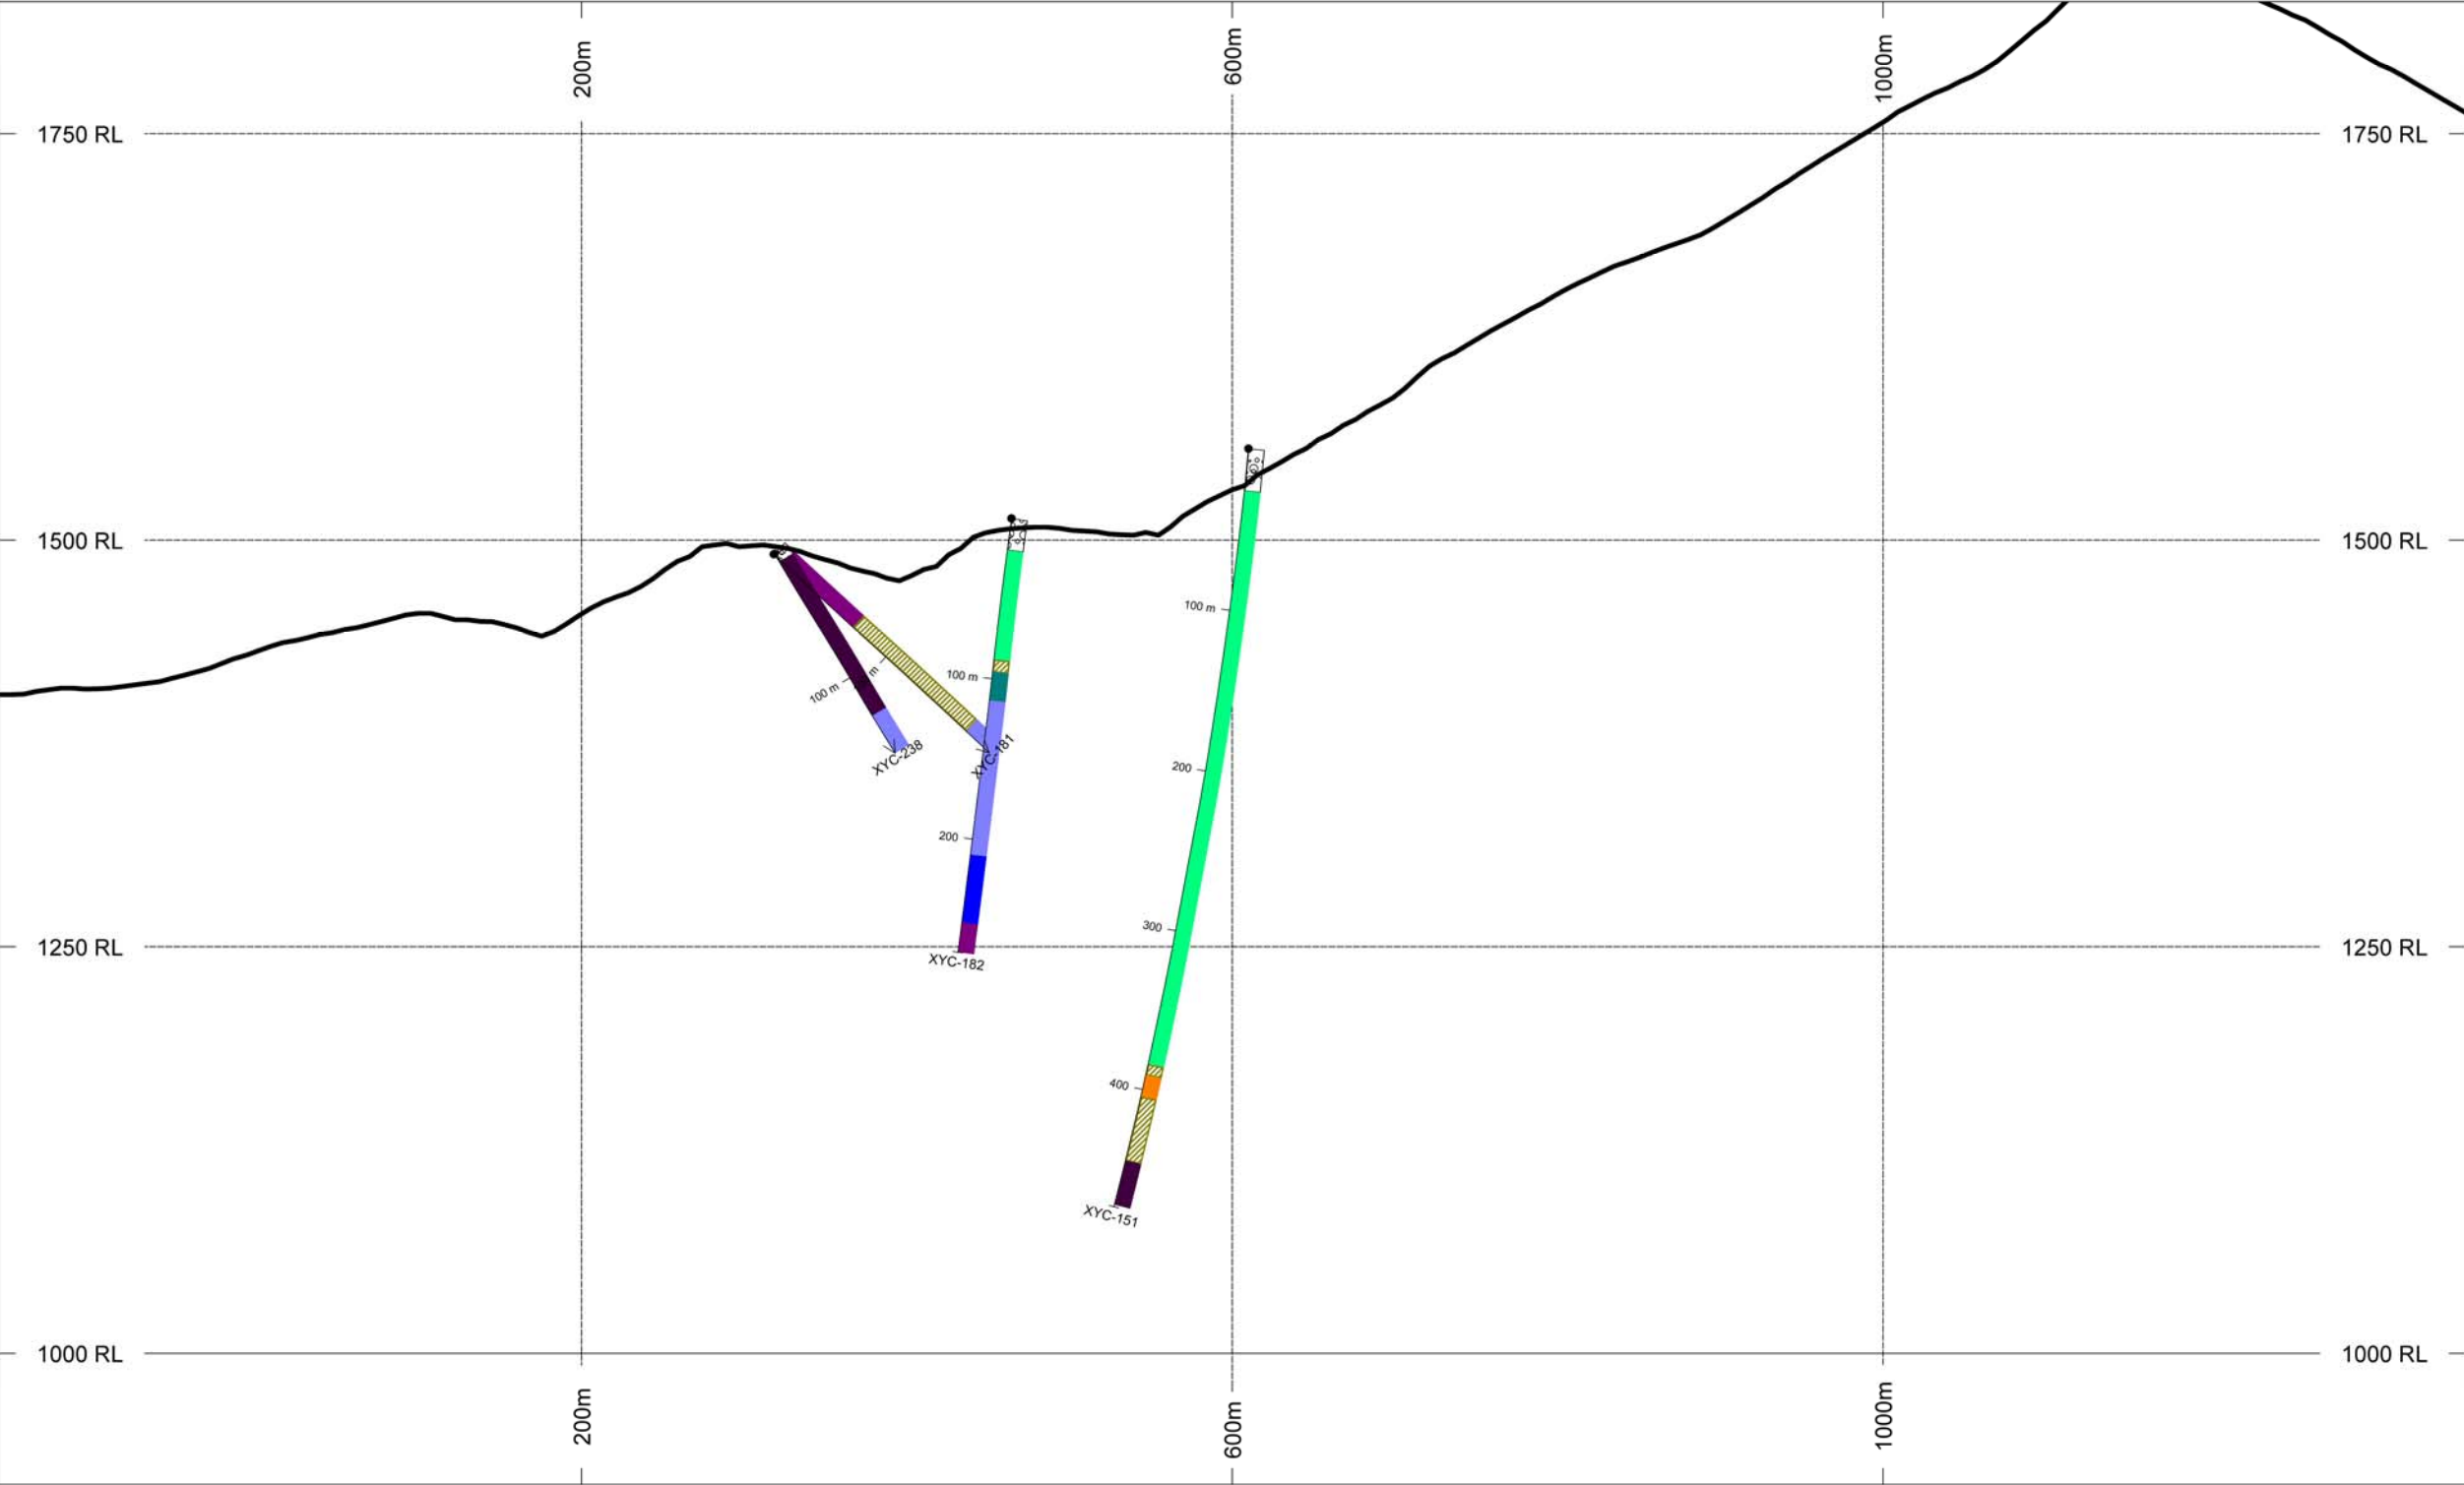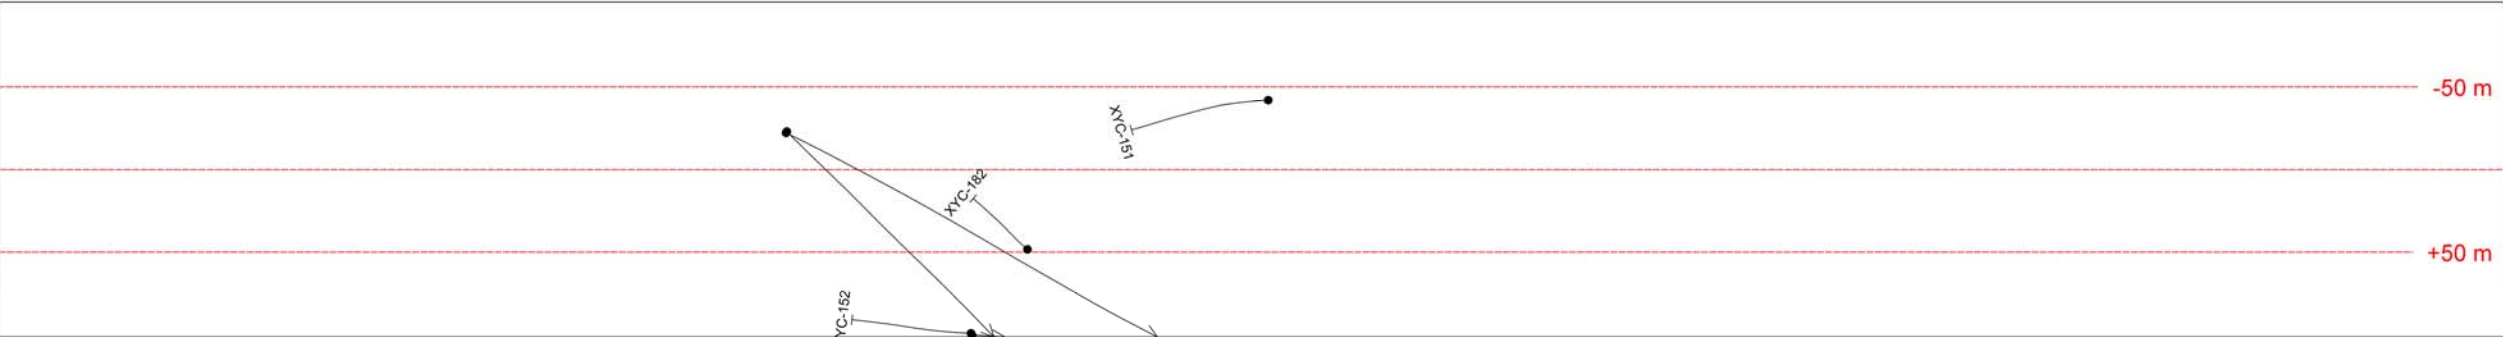

HOLES PLOTTED

TOTAL 4


XYC-151 XYC-181 XYC-182 XYC-238





ROCK CODES	PAT	LABEL	DESCRIPTION
rocktype			
		FECR	Iron Creek Formation
		BSSM	Backside Siliceous Mudstone
		FLMD	Flaggy Mudstone
		USMS	Upper Siliceous Mudstone
		ACTM	Active Member
		LCMS	Lower Cherty Mudstone
		CCMS	Calcareous Mudstone
		PSMS	Pyritic Mudstone
		TRAN	Transition Formation
		CLST	Cambrian Limestone
		OVBR	Overburden
		FLT	Fault
		MDST	Undefined Mudstone

SECTION SPECS:

REF. PT. E, N	488086 m	6927028 m
EXTENTS	1516 m	911.9 m
SECTION TOP, BOT	1831 m	919.3 m
TOLERANCE +/-	50 m	

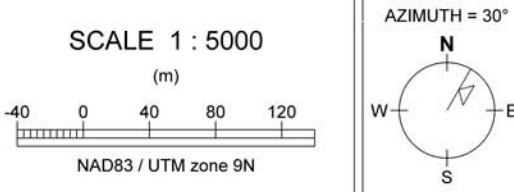

Selwyn Chihong Mining Ltd.
Selwyn Project, YT
Section L_03400N/0600E
XY Central Deposit

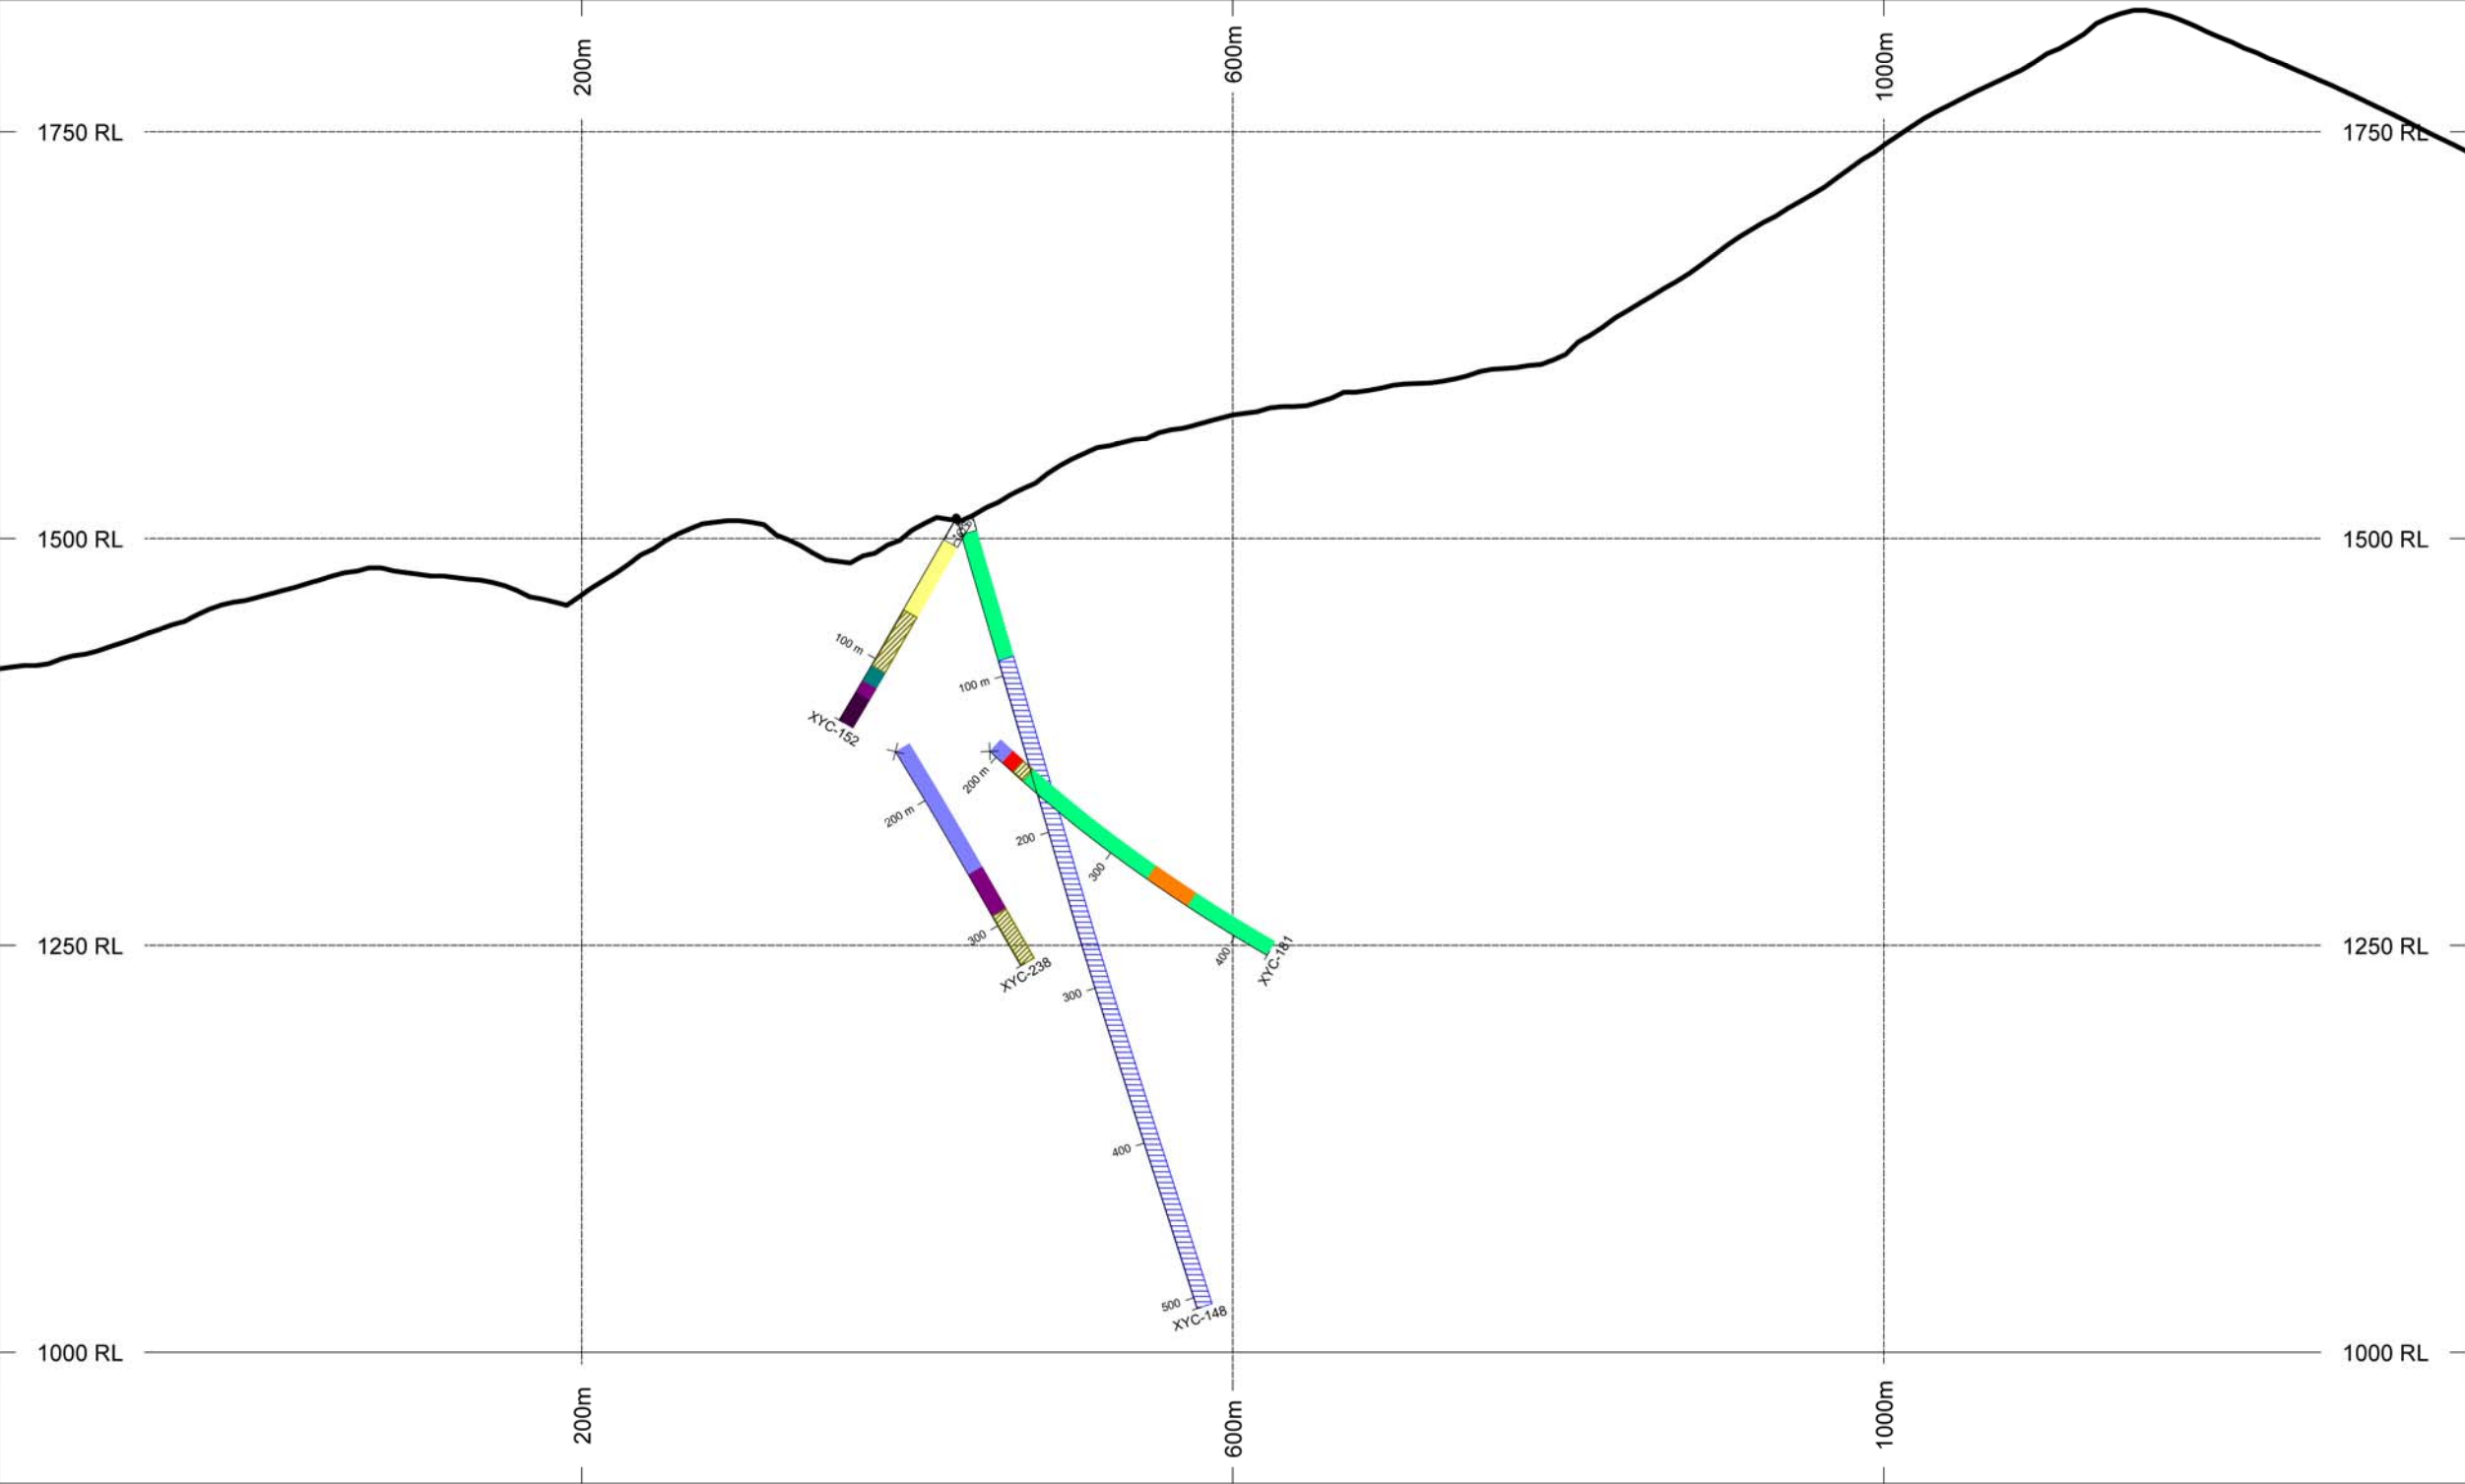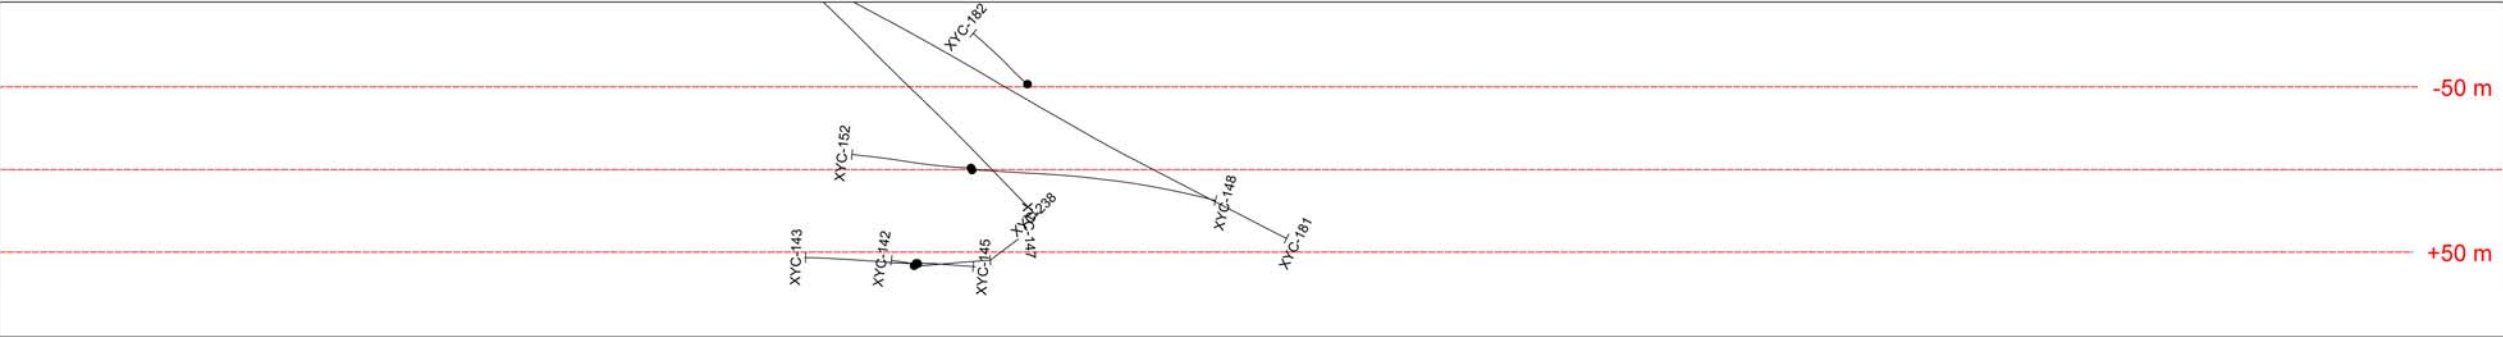

HOLES PLOTTED

TOTAL 4


XYC-148 XYC-152 XYC-181 XYC-238





ROCK CODES	PAT	LABEL	DESCRIPTION
rocktype			
		FECR	Iron Creek Formation
		BSSM	Backside Siliceous Mudstone
		FLMD	Flaggy Mudstone
		USMS	Upper Siliceous Mudstone
		ACTM	Active Member
		LCMS	Lower Cherty Mudstone
		CCMS	Calcareous Mudstone
		PSMS	Pyritic Mudstone
		TRAN	Transition Formation
		CLST	Cambrian Limestone
		OVBR	Overburden
		FLT	Fault
		MDST	Undefined Mudstone

SECTION SPECS:

REF. PT. E, N	488173 m	6926978 m
EXTENTS	1516 m	911.9 m
SECTION TOP, BOT	1831 m	919.3 m
TOLERANCE +/-	50 m	

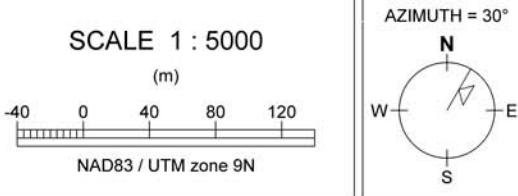

Selwyn Chihong Mining Ltd.
Selwyn Project, YT
Section L_03300N/0600E
XY Central Deposit

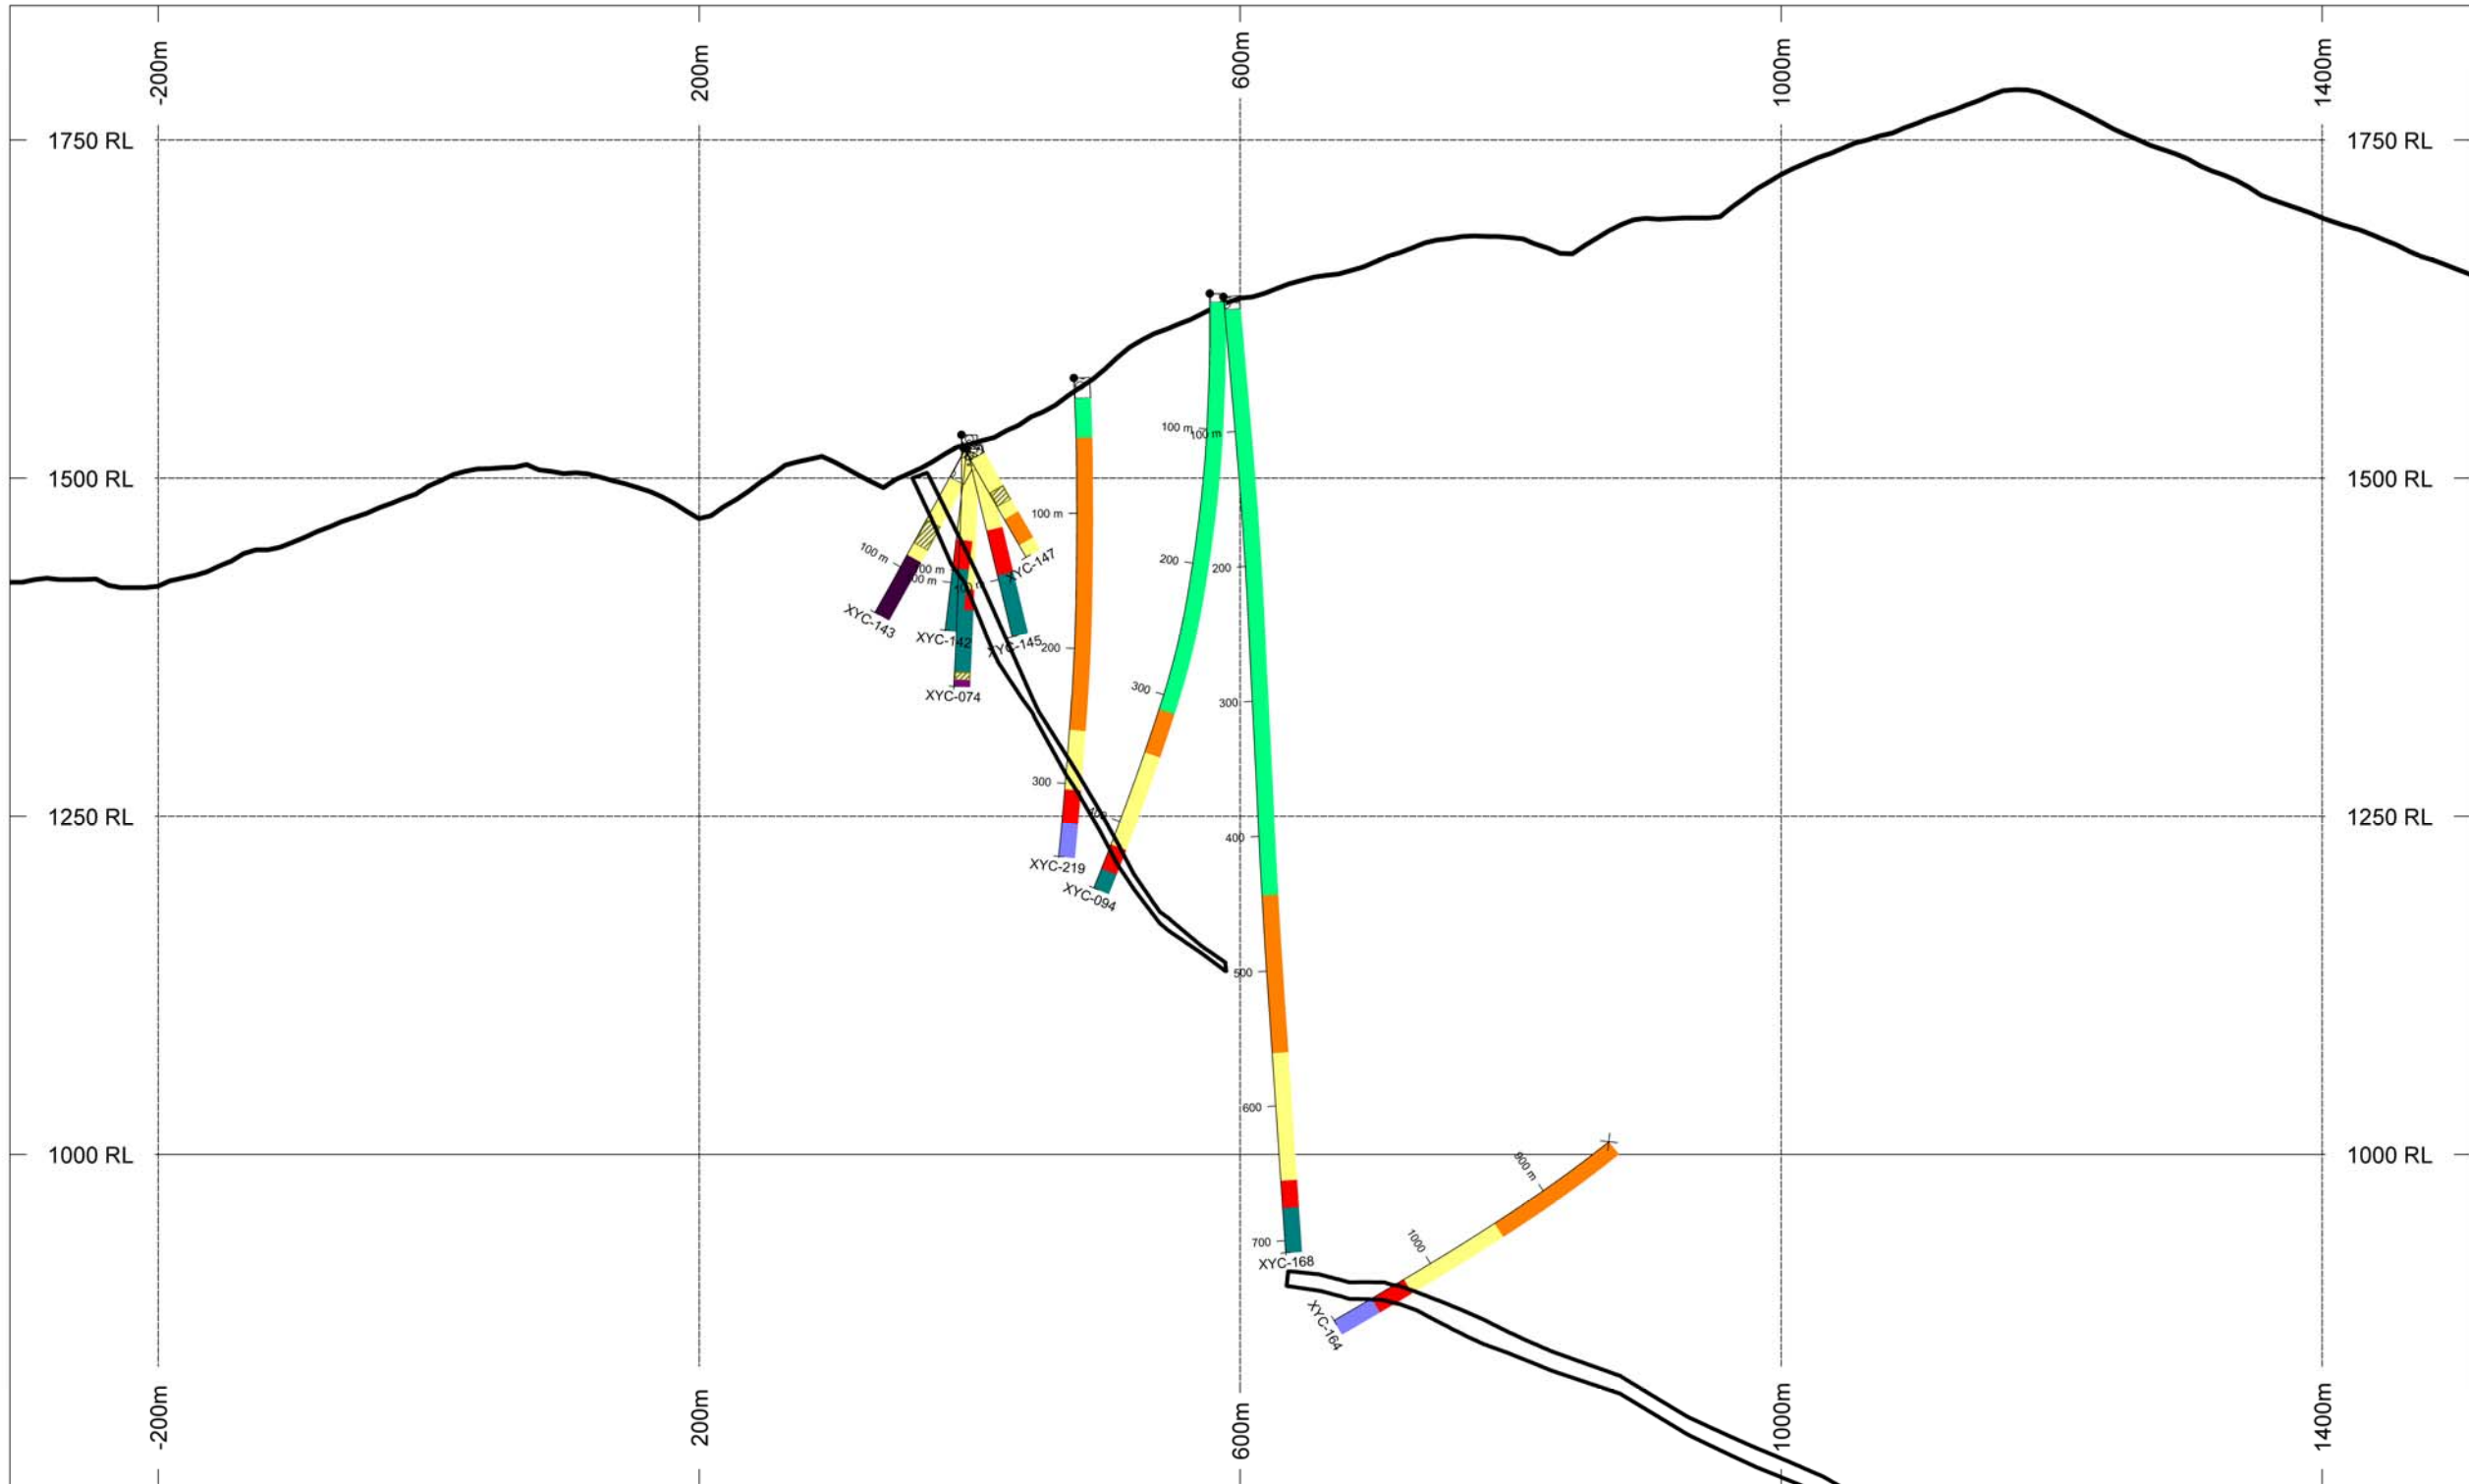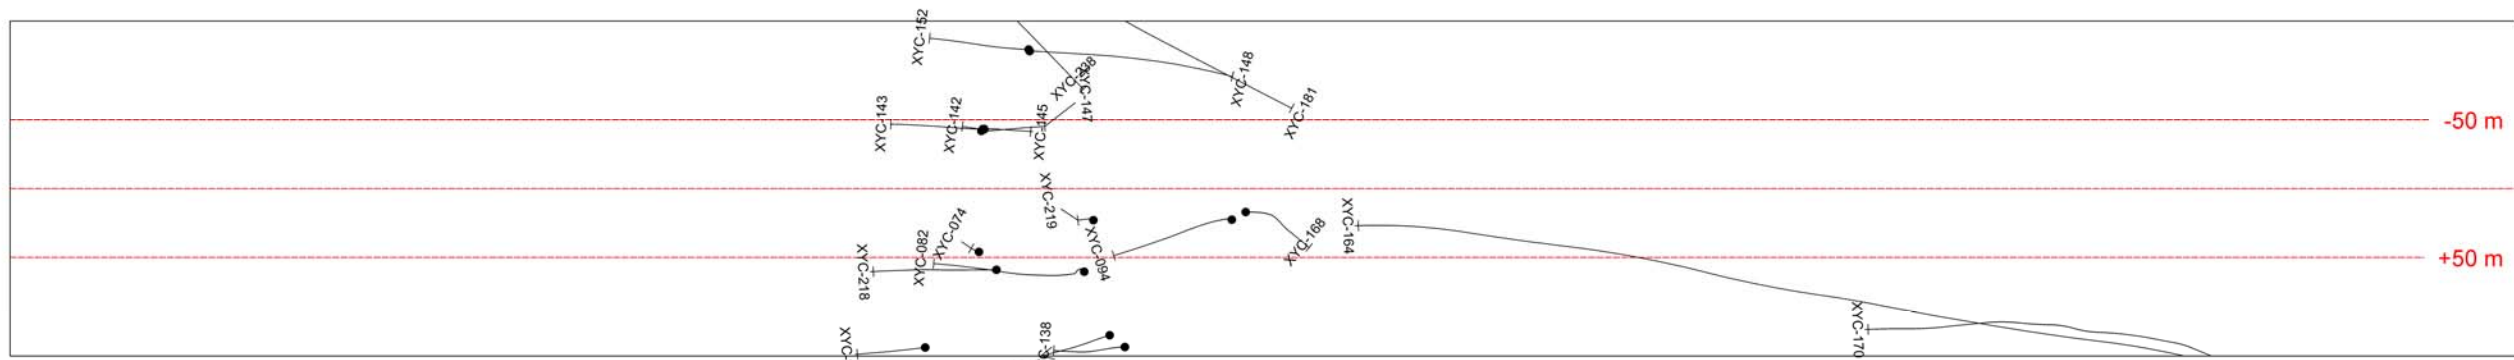

HOLES PLOTTED

TOTAL 9


XYC-074	XYC-094	XYC-142	XYC-143
XYC-145	XYC-147	XYC-164	XYC-168
XYC-219			





ROCK CODES	PAT	LABEL	DESCRIPTION
rocktype			
		BSSM	Backside Siliceous Mudstone
		FLMD	Flaggy Mudstone
		USMS	Upper Siliceous Mudstone
		ACTM	Active Member
		LCMS	Lower Cherty Mudstone
		CCMS	Calcareous Mudstone
		TRAN	Transition Formation
		CLST	Cambrian Limestone
		OVBR	Overburden
		FLT	Fault

SECTION SPECS:

REF. PT. E, N	488260 m	6926928 m
EXTENTS	1819 m	1094 m
SECTION TOP, BOT	1849 m	755.2 m
TOLERANCE +/-	50 m	

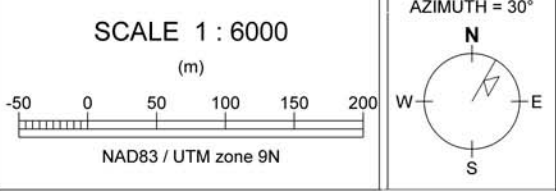

Selwyn Chihong Mining Ltd.
Selwyn Project, YT
Section L_03200N/0600E
XY Central Deposit

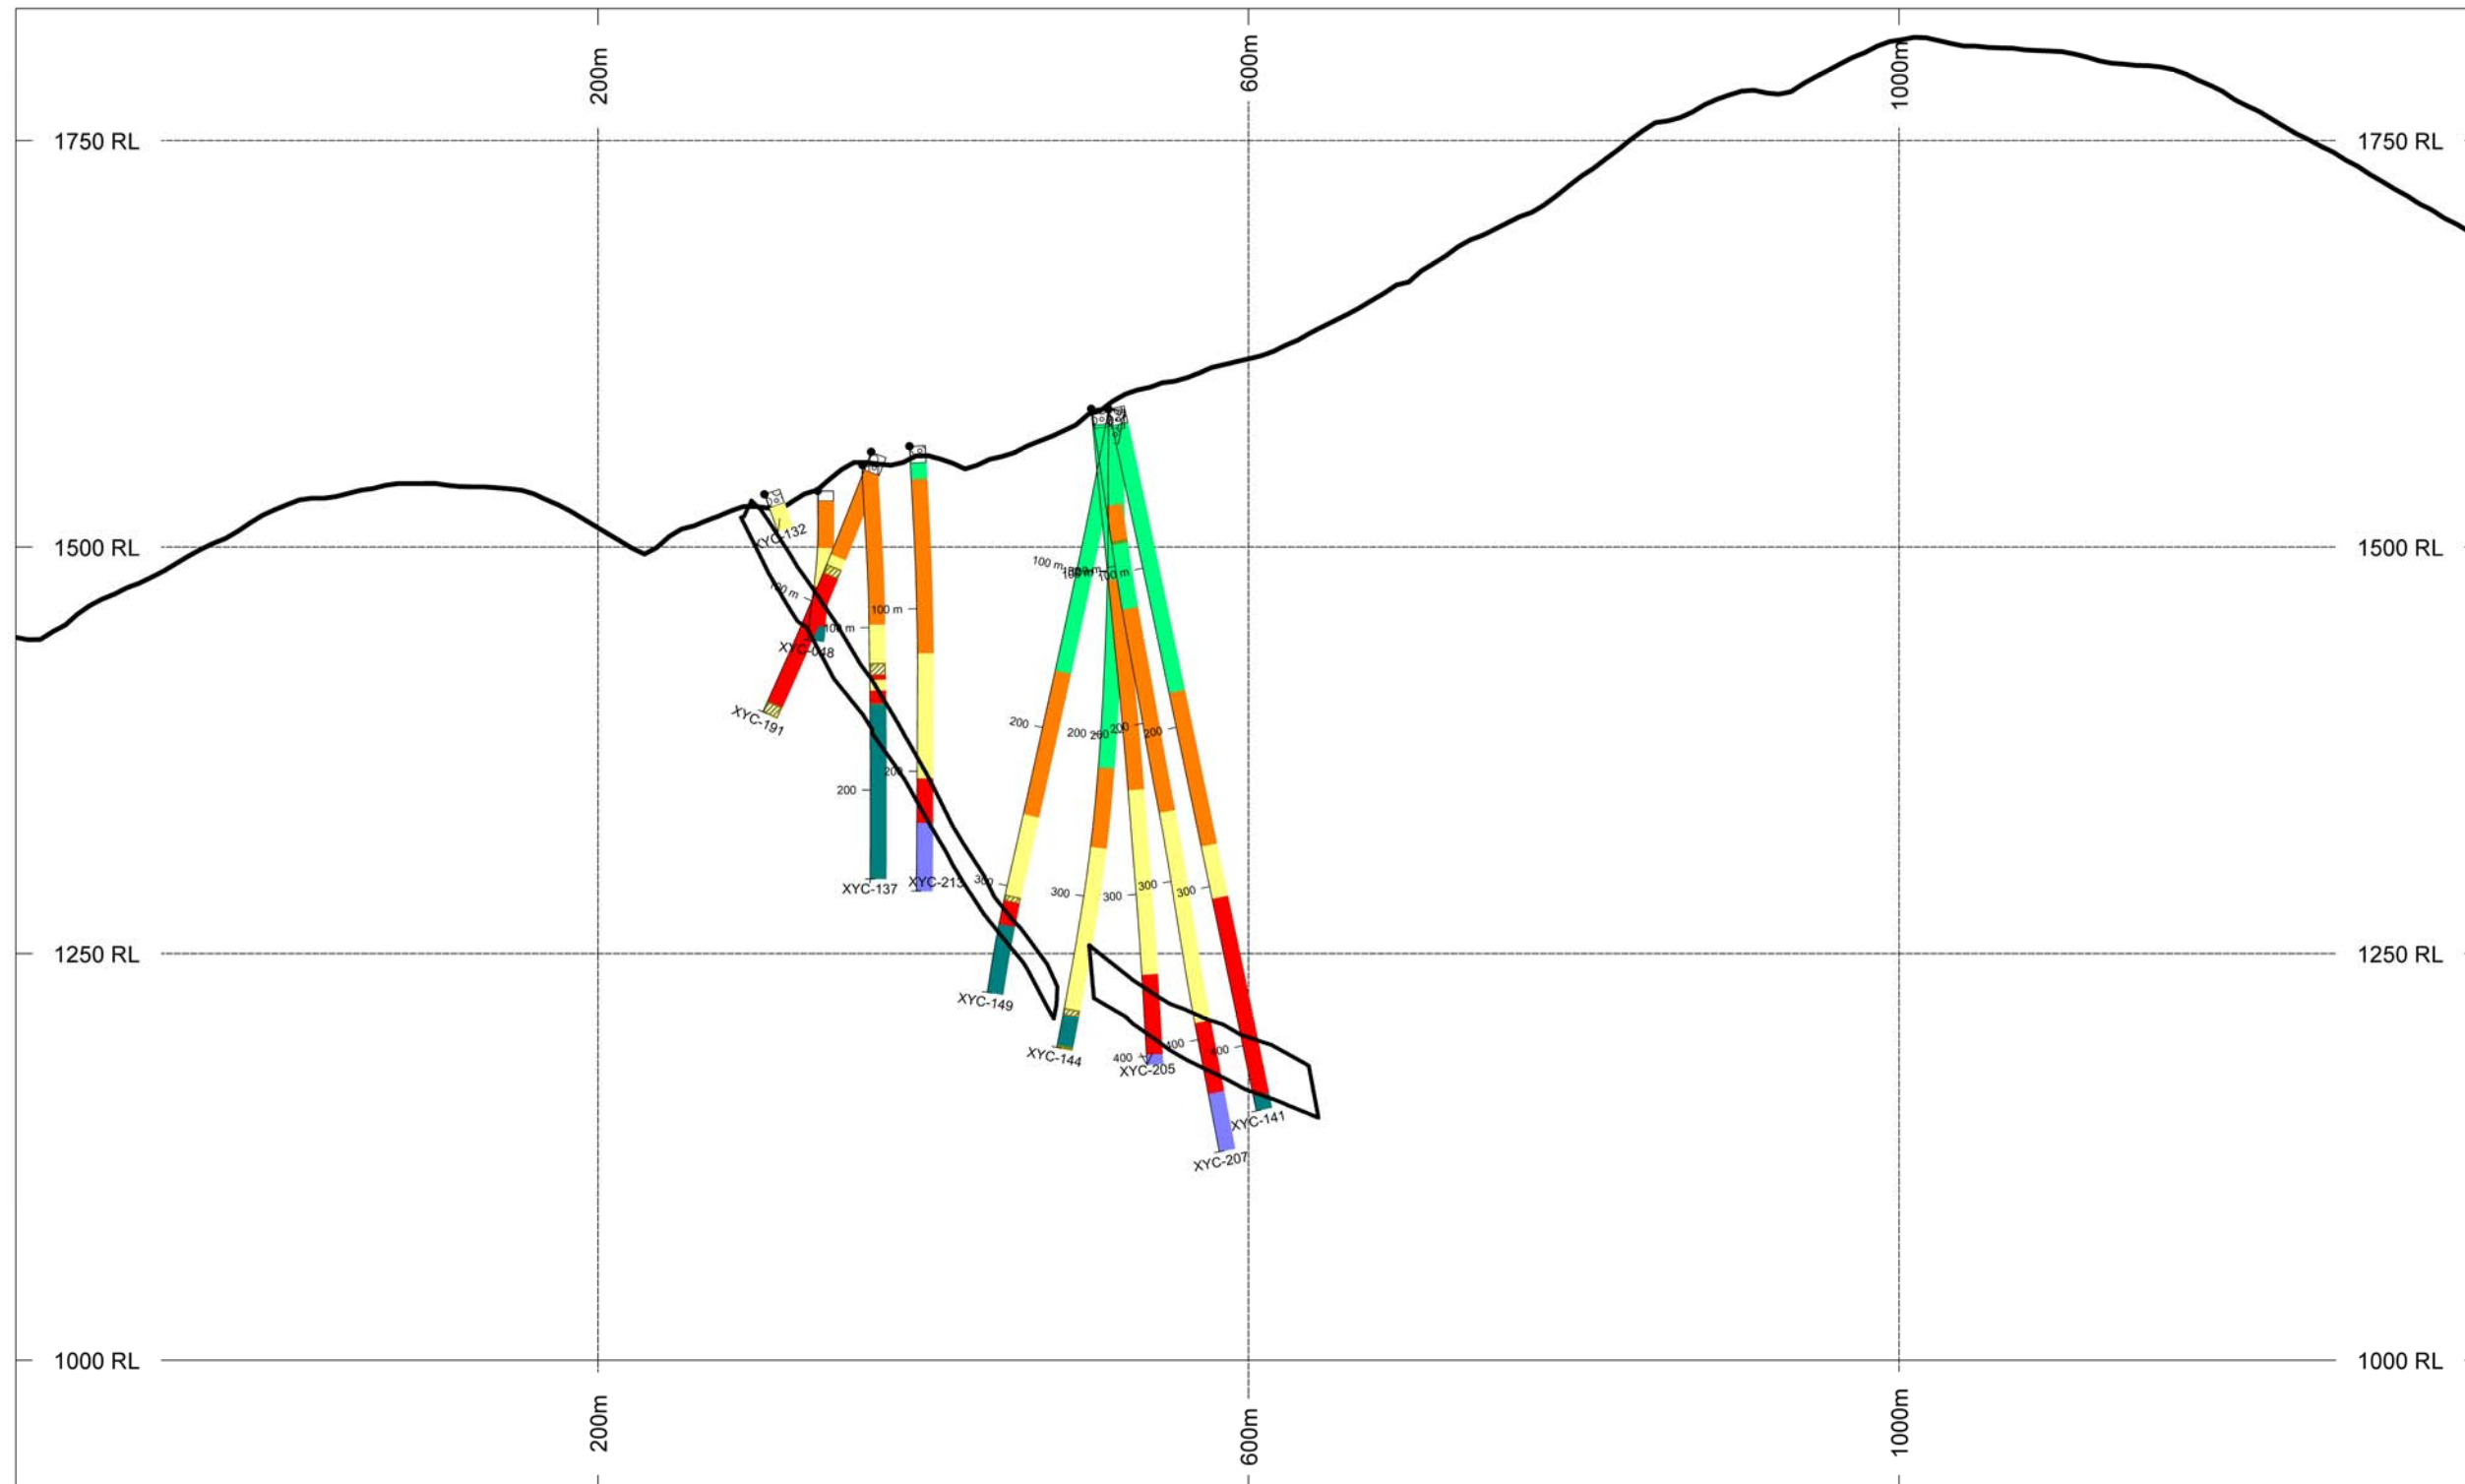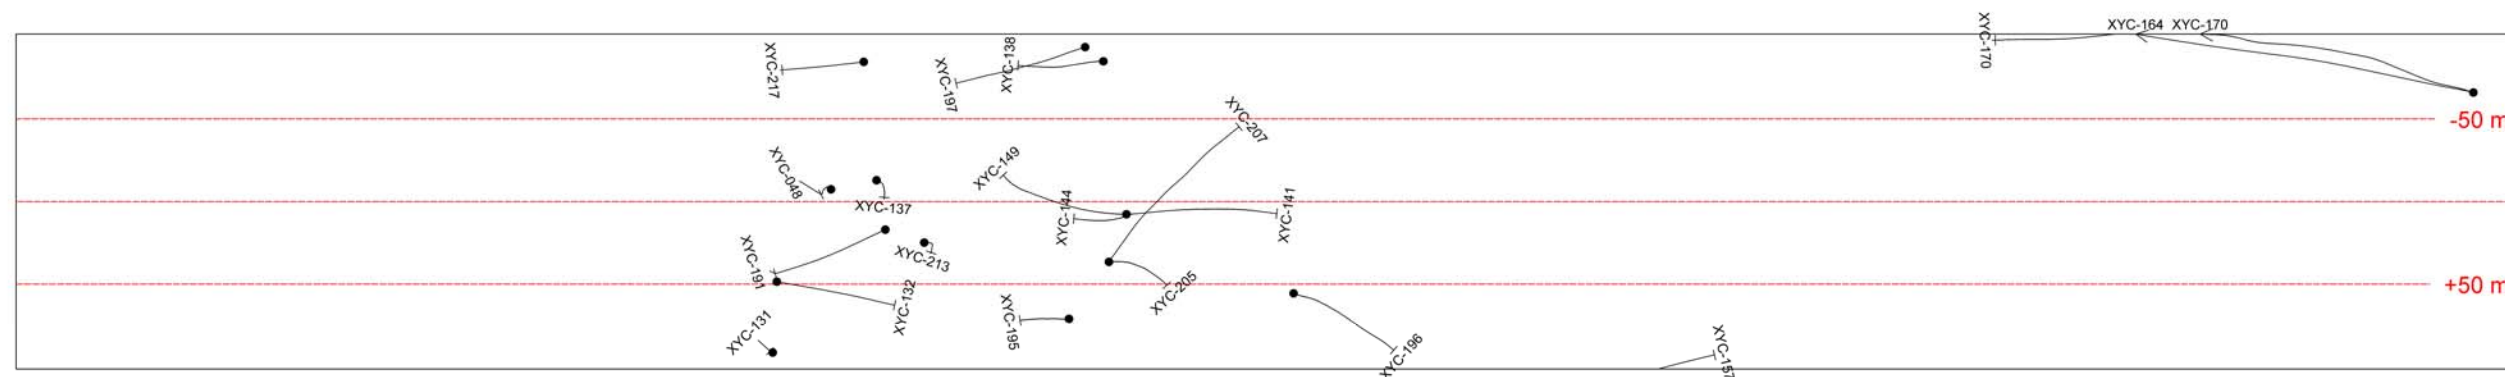

HOLES PLOTTED

TOTAL 10

XYC-048	XYC-132	XYC-137	XYC-141
XYC-144	XYC-149	XYC-191	XYC-205
XYC-207	XYC-213		





SELWYN CHIHONG
MINING LTD.

ROCK CODES	PAT	LABEL	DESCRIPTION
rocktype		FECR	Iron Creek Formation
		BSSM	Backside Siliceous Mudstone
		FLMD	Flaggy Mudstone
		USMS	Upper Siliceous Mudstone
		ACTM	Active Member
		LCMS	Lower Cherty Mudstone
		CCMS	Calcareous Mudstone
		PSMS	Pyritic Mudstone
		TRAN	Transition Formation
		CLST	Cambrian Limestone
		OVBR	Overburden
		FLT	Fault
		MDST	Undefined Mudstone

SECTION SPECS:

REF. PT. E, N	488433 m	6926828 m
EXTENTS	1516 m	911.9 m
SECTION TOP, BOT	1831 m	919.3 m
TOLERANCE +/-	50 m	


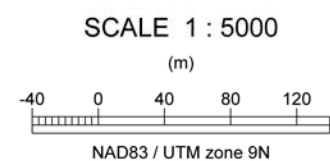


Selwyn Chihong Mining Ltd.

Selwyn Project, YT

Section L_03000N/0600E

XY Central Deposit

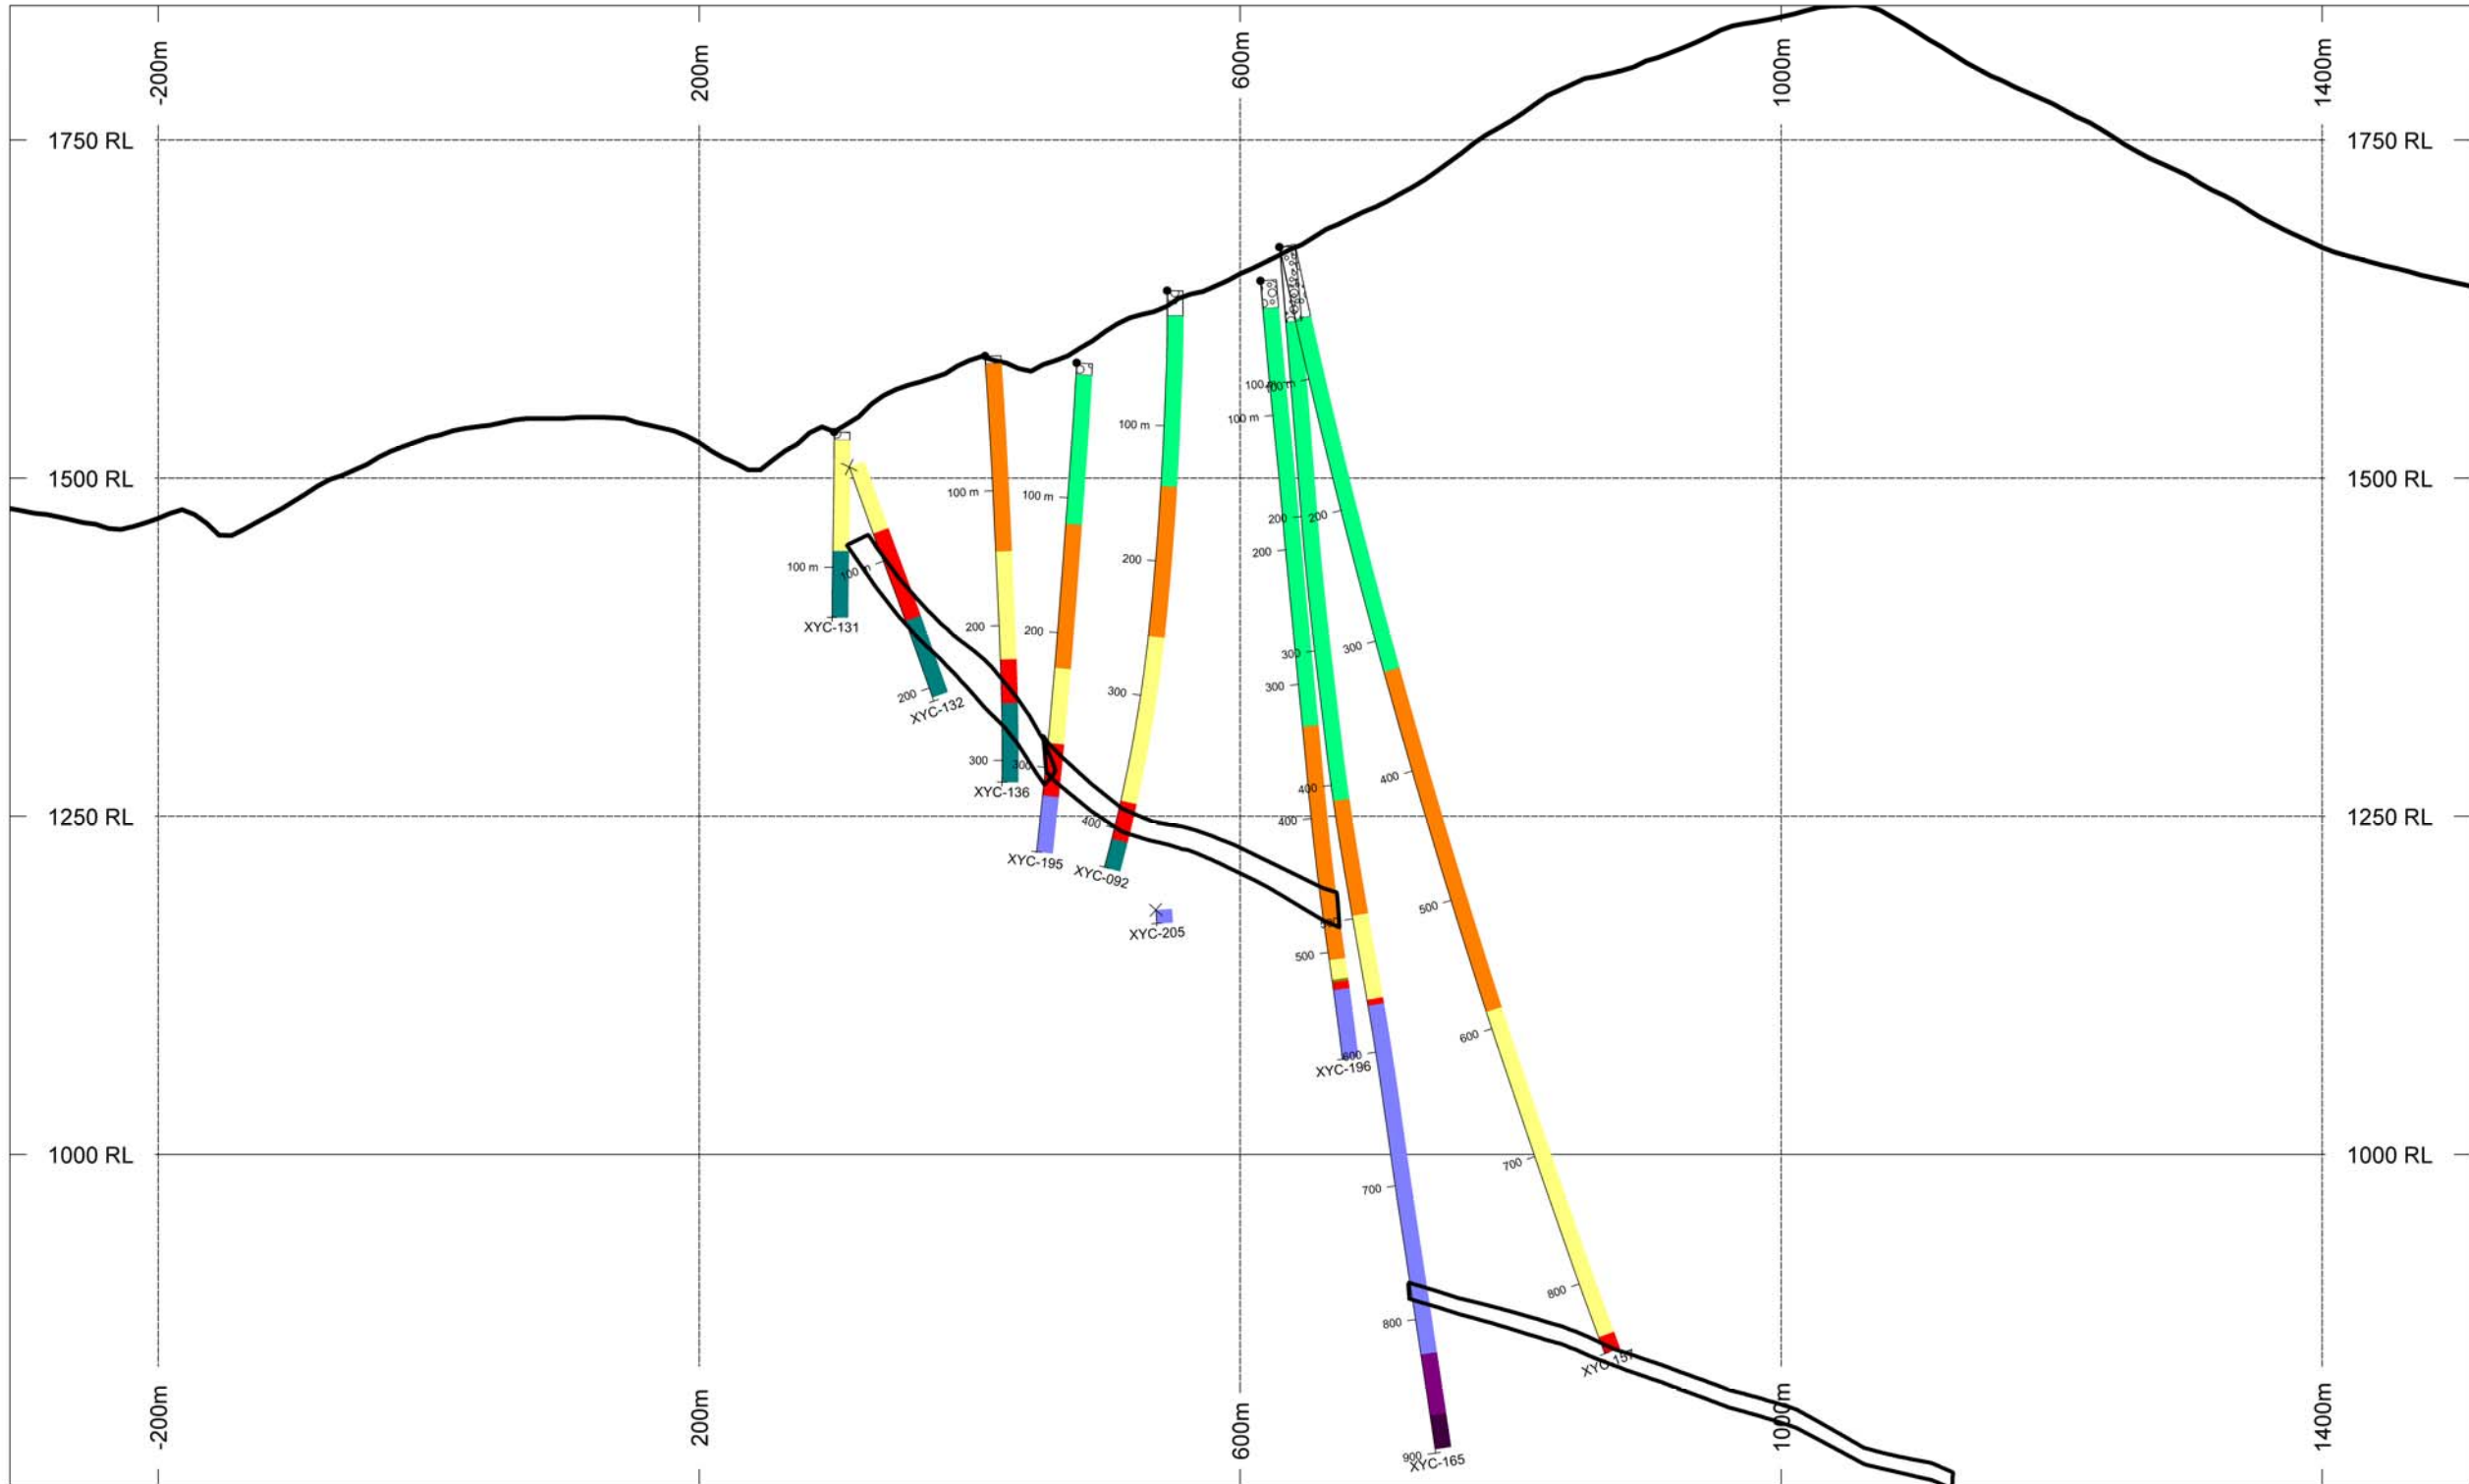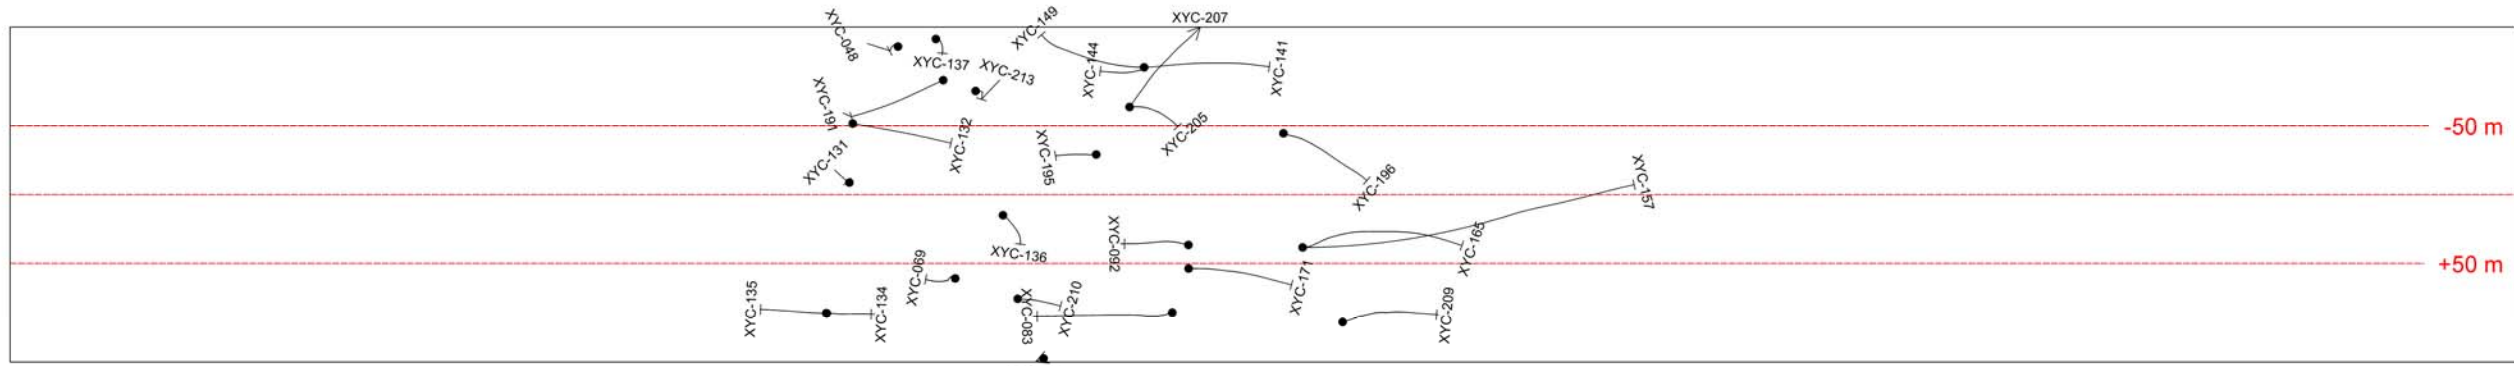

HOLES PLOTTED

TOTAL 9


XYZ-092	XYZ-131	XYZ-132	XYZ-136
XYZ-157	XYZ-165	XYZ-195	XYZ-196
XYZ-205			




ROCK CODES	PAT	LABEL	DESCRIPTION
rocktype			
		BSSM	Backside Siliceous Mudstone
		FLMD	Flaggy Mudstone
		USMS	Upper Siliceous Mudstone
		ACTM	Active Member
		LCMS	Lower Cherty Mudstone
		CCMS	Calcareous Mudstone
		TRAN	Transition Formation
		CLST	Cambrian Limestone
		OVBR	Overburden
		FLT	Fault

SECTION SPECS:

REF. PT. E, N	488519 m	6926778 m
EXTENTS	1819 m	1094 m
SECTION TOP, BOT	1849 m	755.2 m
TOLERANCE +/-	50 m	

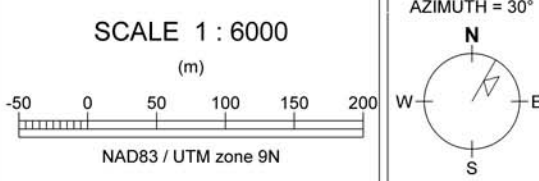

Selwyn Chihong Mining Ltd.
Selwyn Project, YT
Section L_02900N/0600E
XY Central Deposit

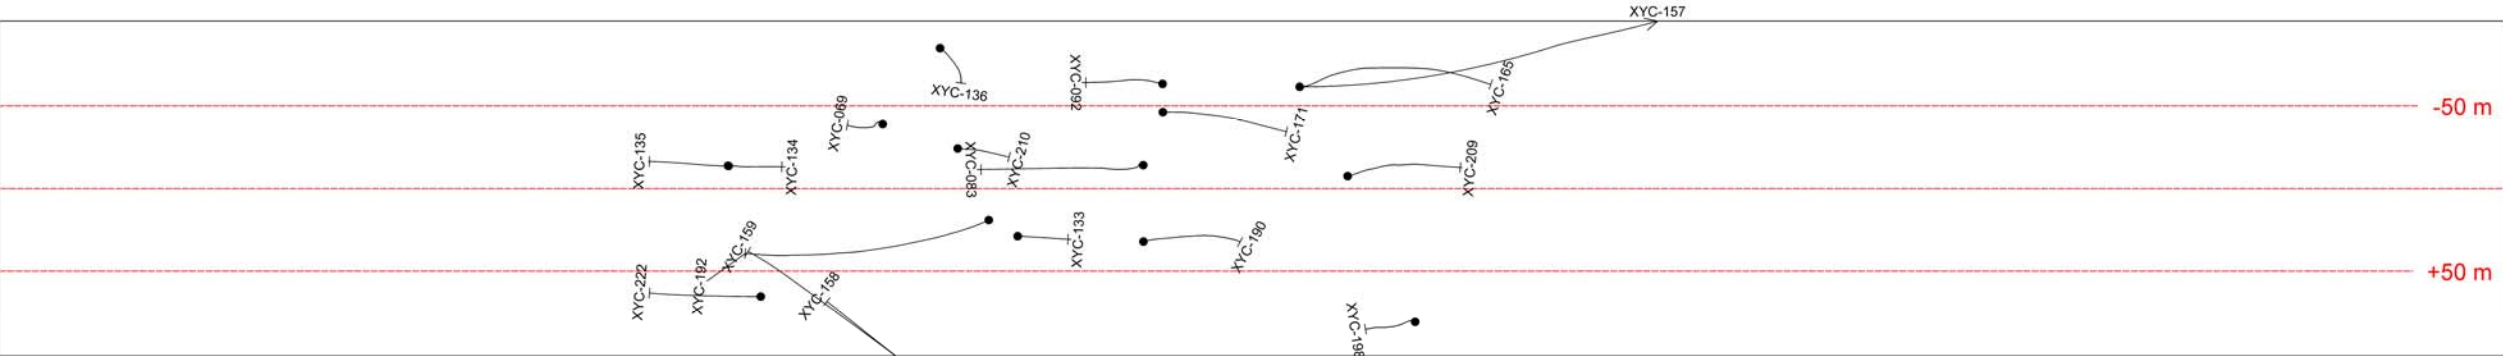


HOLES PLOTTED

TOTAL 11

XYC-069	XYC-083	XYC-133	XYC-134
XYC-135	XYC-159	XYC-171	XYC-190
XYC-192	XYC-209	XYC-210	





SELWYN CHIHONG
MINING LTD.

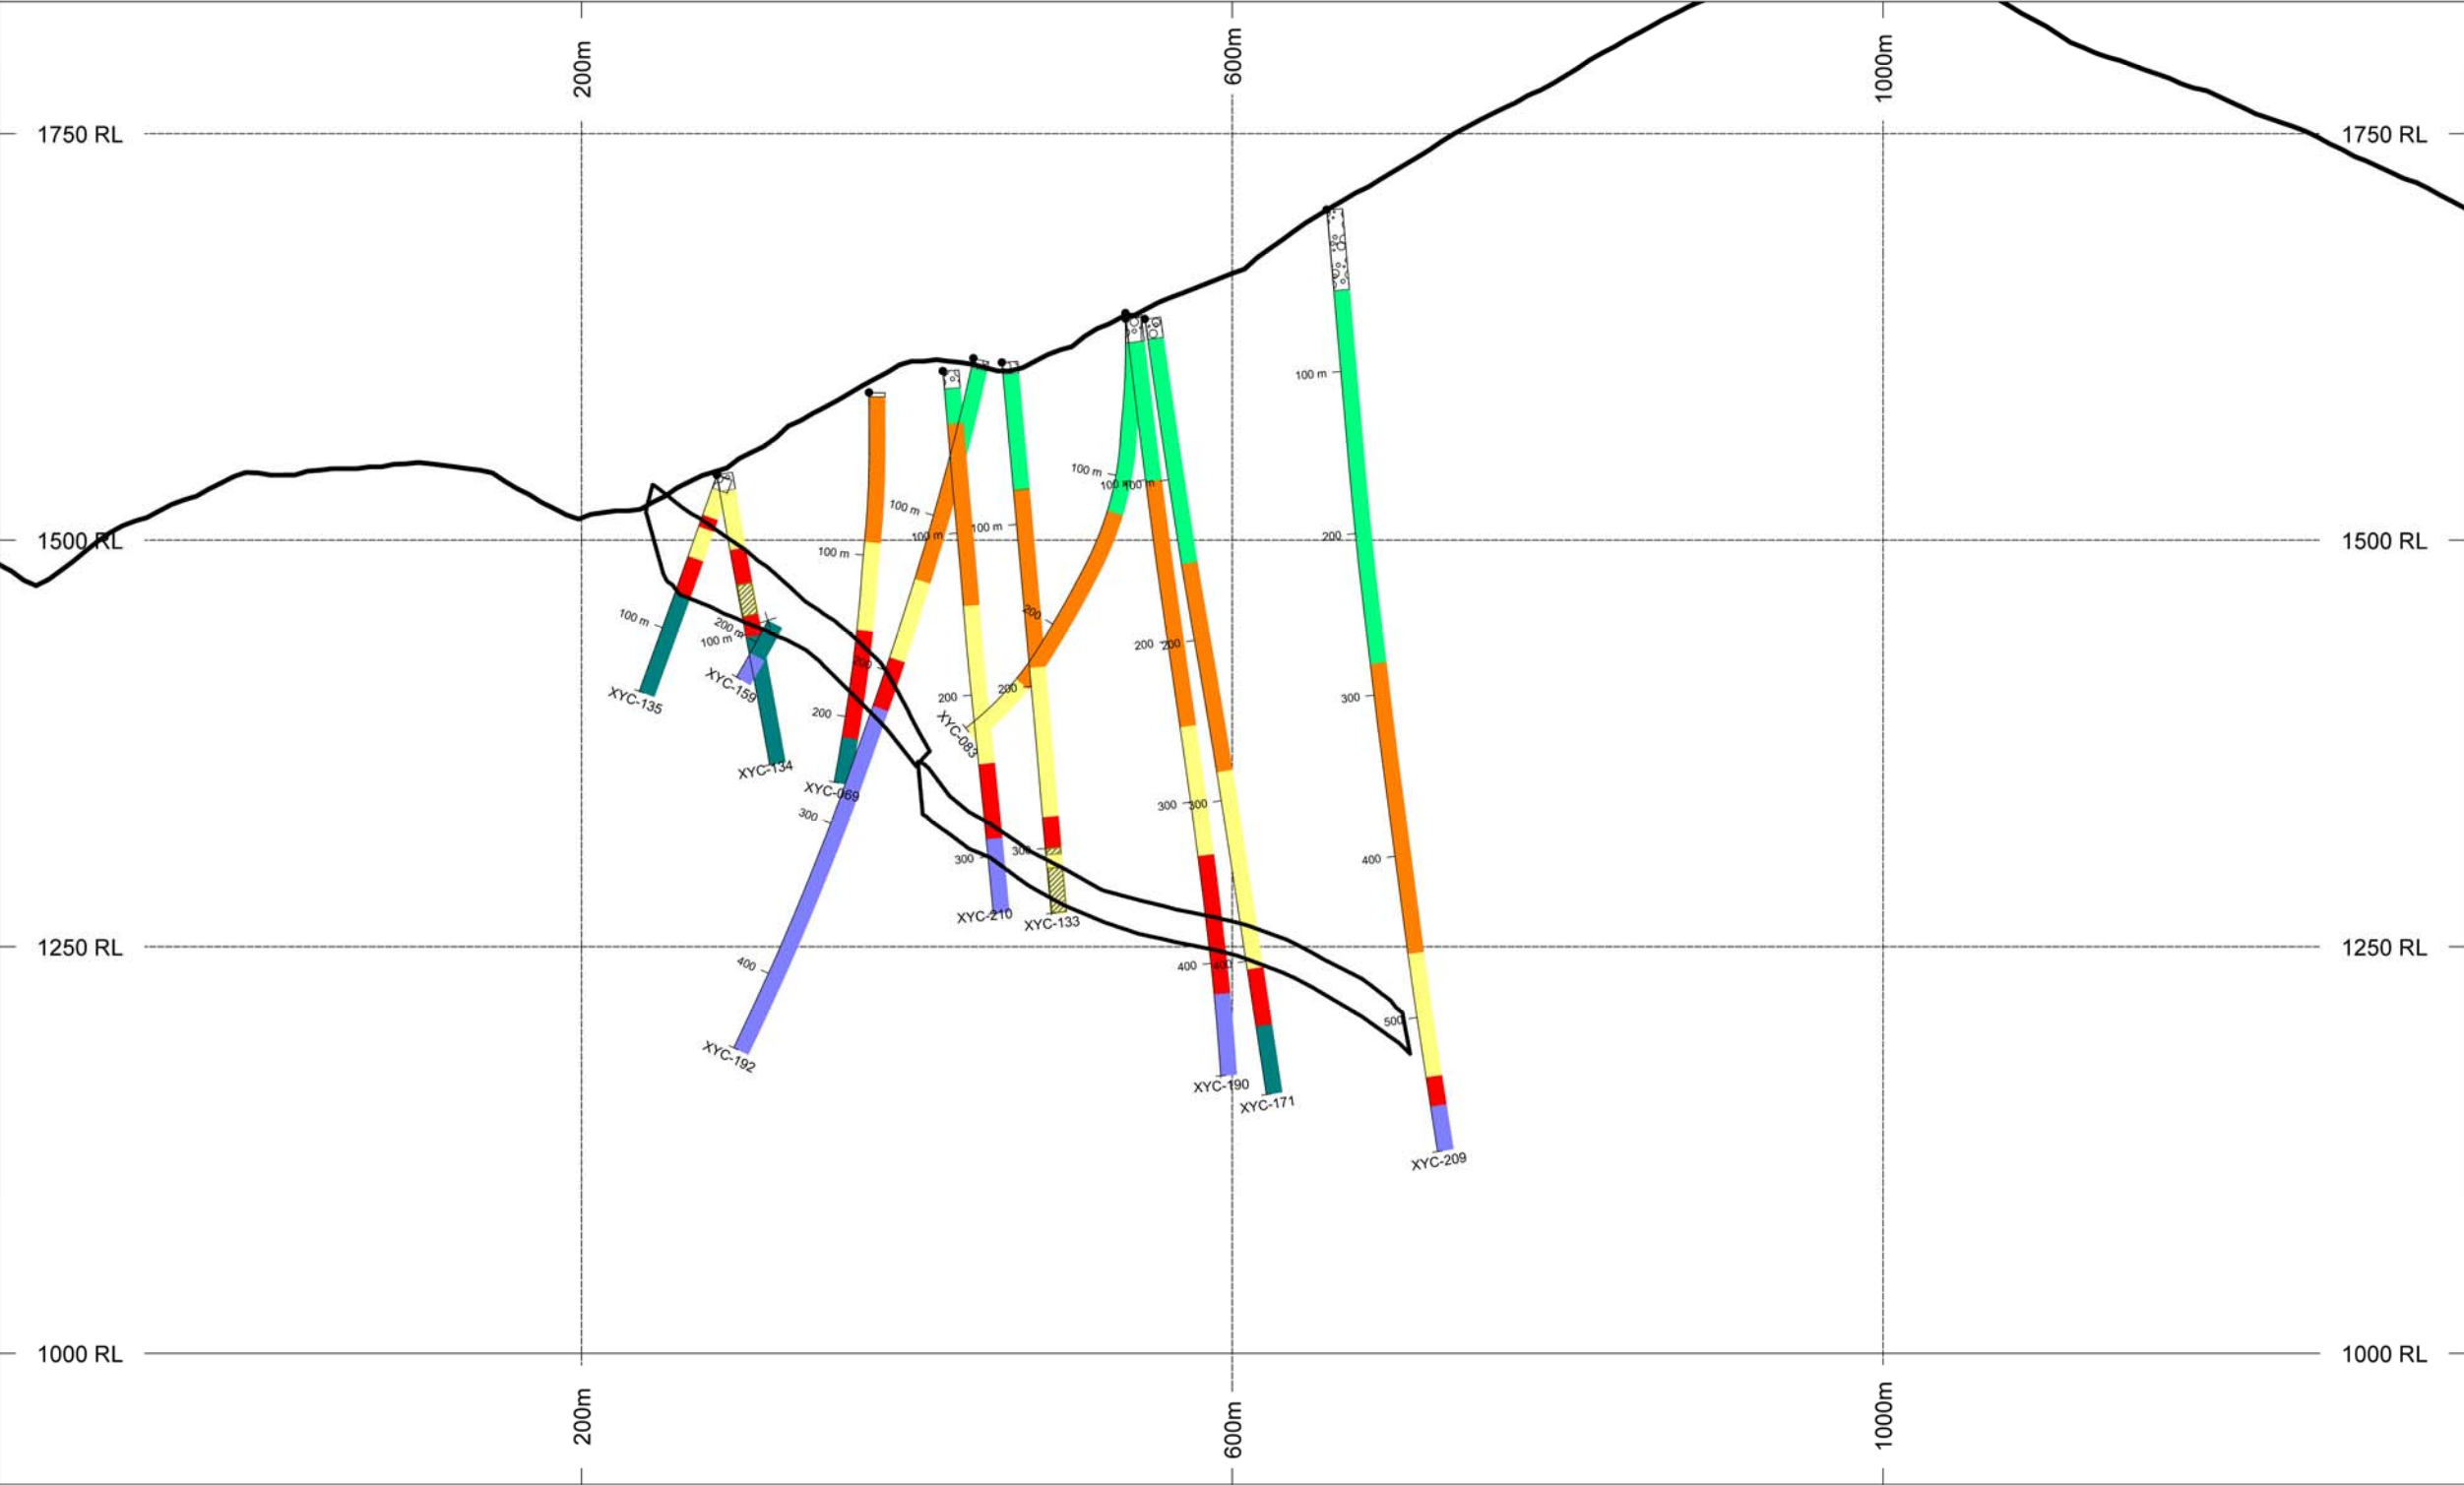



ROCK CODES	PAT	LABEL	DESCRIPTION
rocktype			
		FECR	Iron Creek Formation
		BSSM	Backside Siliceous Mudstone
		FLMD	Flaggy Mudstone
		USMS	Upper Siliceous Mudstone
		ACTM	Active Member
		LCMS	Lower Cherty Mudstone
		CCMS	Calcareous Mudstone
		PSMS	Pyritic Mudstone
		TRAN	Transition Formation
		CLST	Cambrian Limestone
		OVBR	Overburden
		FLT	Fault
		MDST	Undefined Mudstone

SECTION SPECS:

REF. PT. E, N	488606	6926728
EXTENTS	1516	911.9
SECTION TOP, BOT	1831	919.3
TOLERANCE +/-	50	

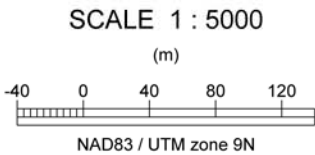

Selwyn Chihong Mining Ltd.
Selwyn Project, YT
Section L_02800N/0600E
XY Central Deposit

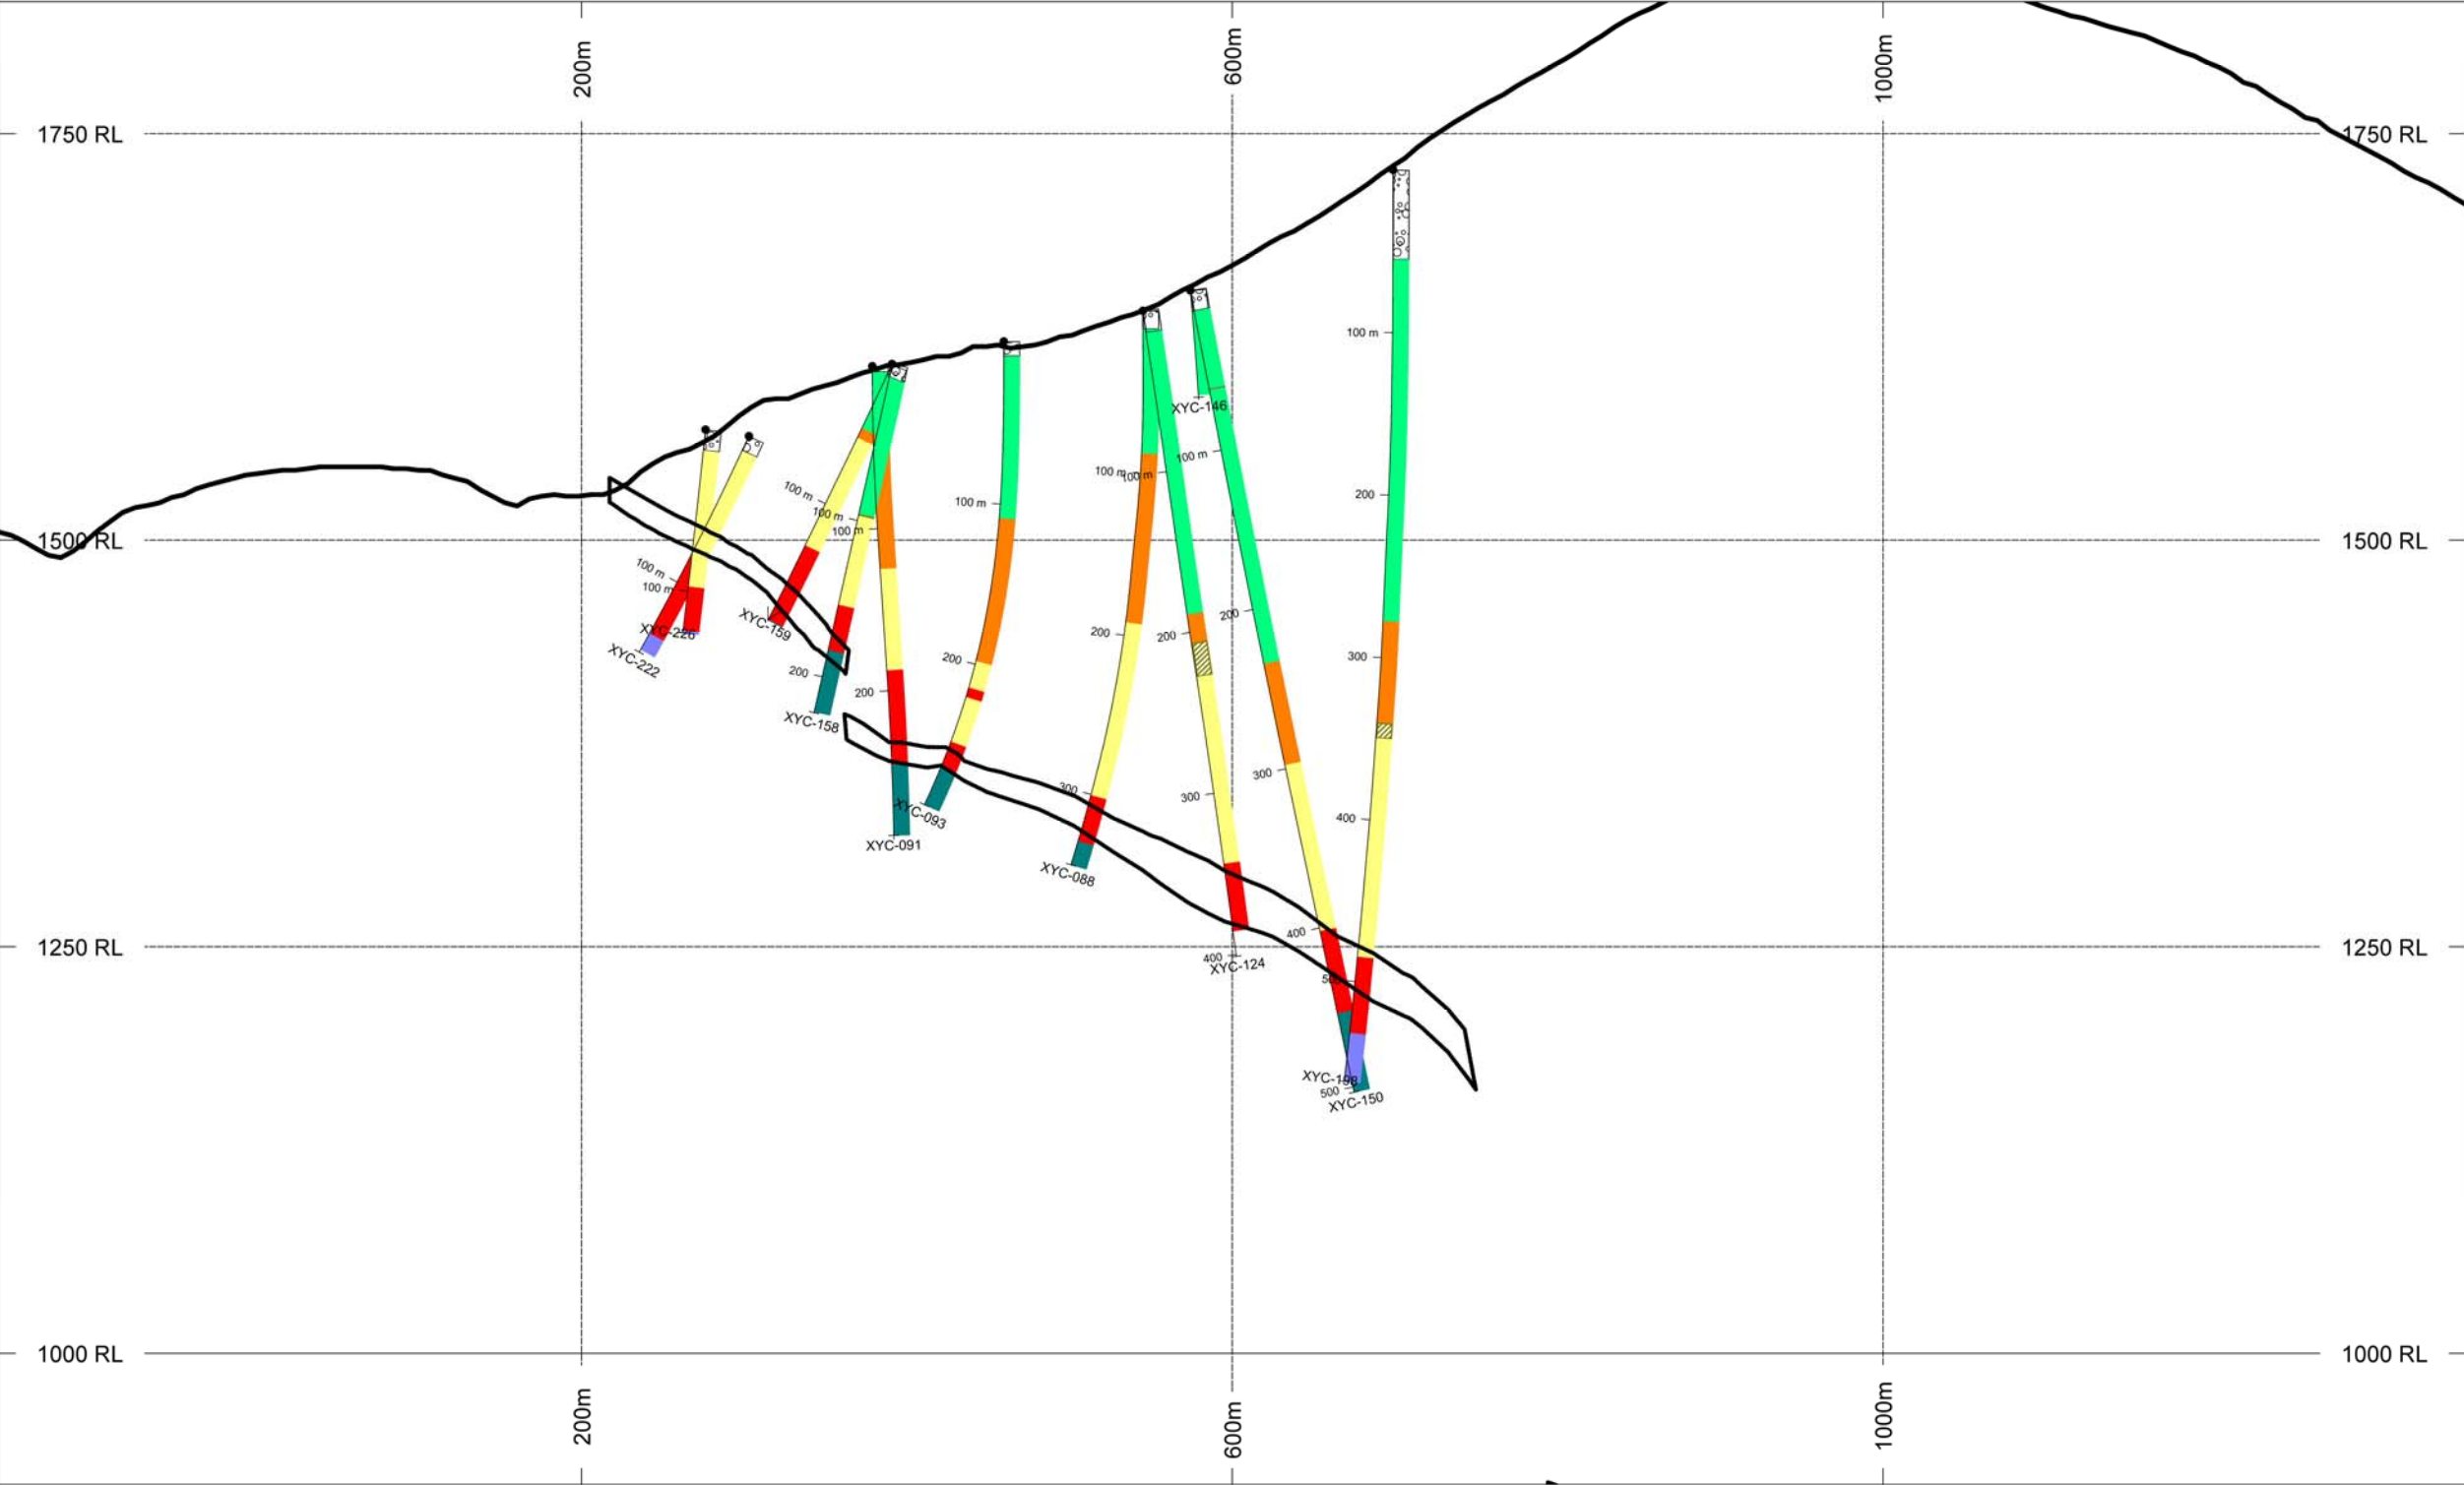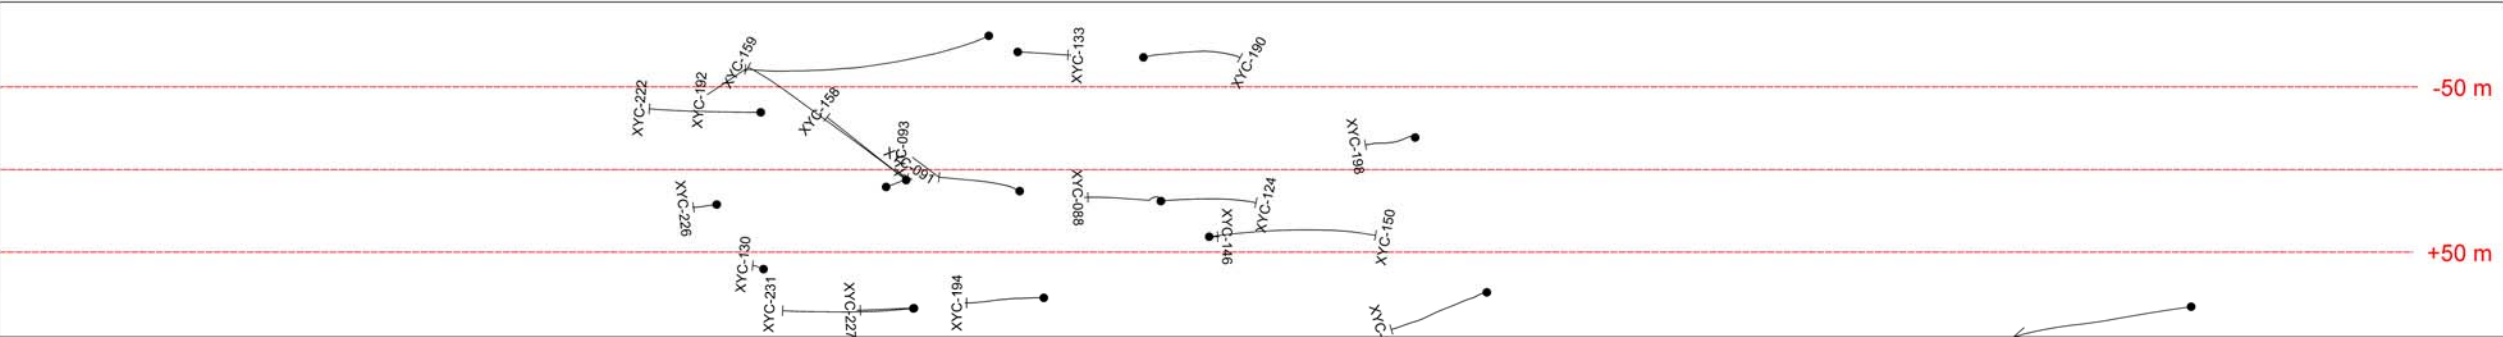

HOLES PLOTTED

TOTAL 11

XYC-088	XYC-091	XYC-093	XYC-124
XYC-146	XYC-150	XYC-158	XYC-159
XYC-198	XYC-222	XYC-226	




SELWYN CHIHONG
MINING LTD.



ROCK CODES	PAT	LABEL	DESCRIPTION
rocktype			
		FECR	Iron Creek Formation
		BSSM	Backside Siliceous Mudstone
		FLMD	Flaggy Mudstone
		USMS	Upper Siliceous Mudstone
		ACTM	Active Member
		LCMS	Lower Cherty Mudstone
		CCMS	Calcareous Mudstone
		PSMS	Pyritic Mudstone
		TRAN	Transition Formation
		CLST	Cambrian Limestone
		OVBR	Overburden
		FLT	Fault
		MDST	Undefined Mudstone

SECTION SPECS:

REF. PT. E, N	488693 m	6926678 m
EXTENTS	1516 m	911.9 m
SECTION TOP, BOT	1831 m	919.3 m
TOLERANCE +/-	50 m	

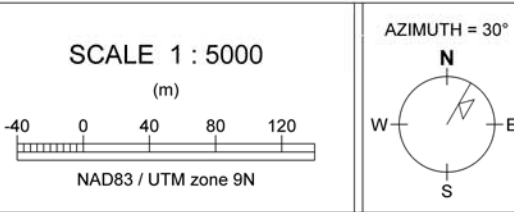

Selwyn Chihong Mining Ltd.
Selwyn Project, YT
Section L_02700N/0600E
XY Central Deposit

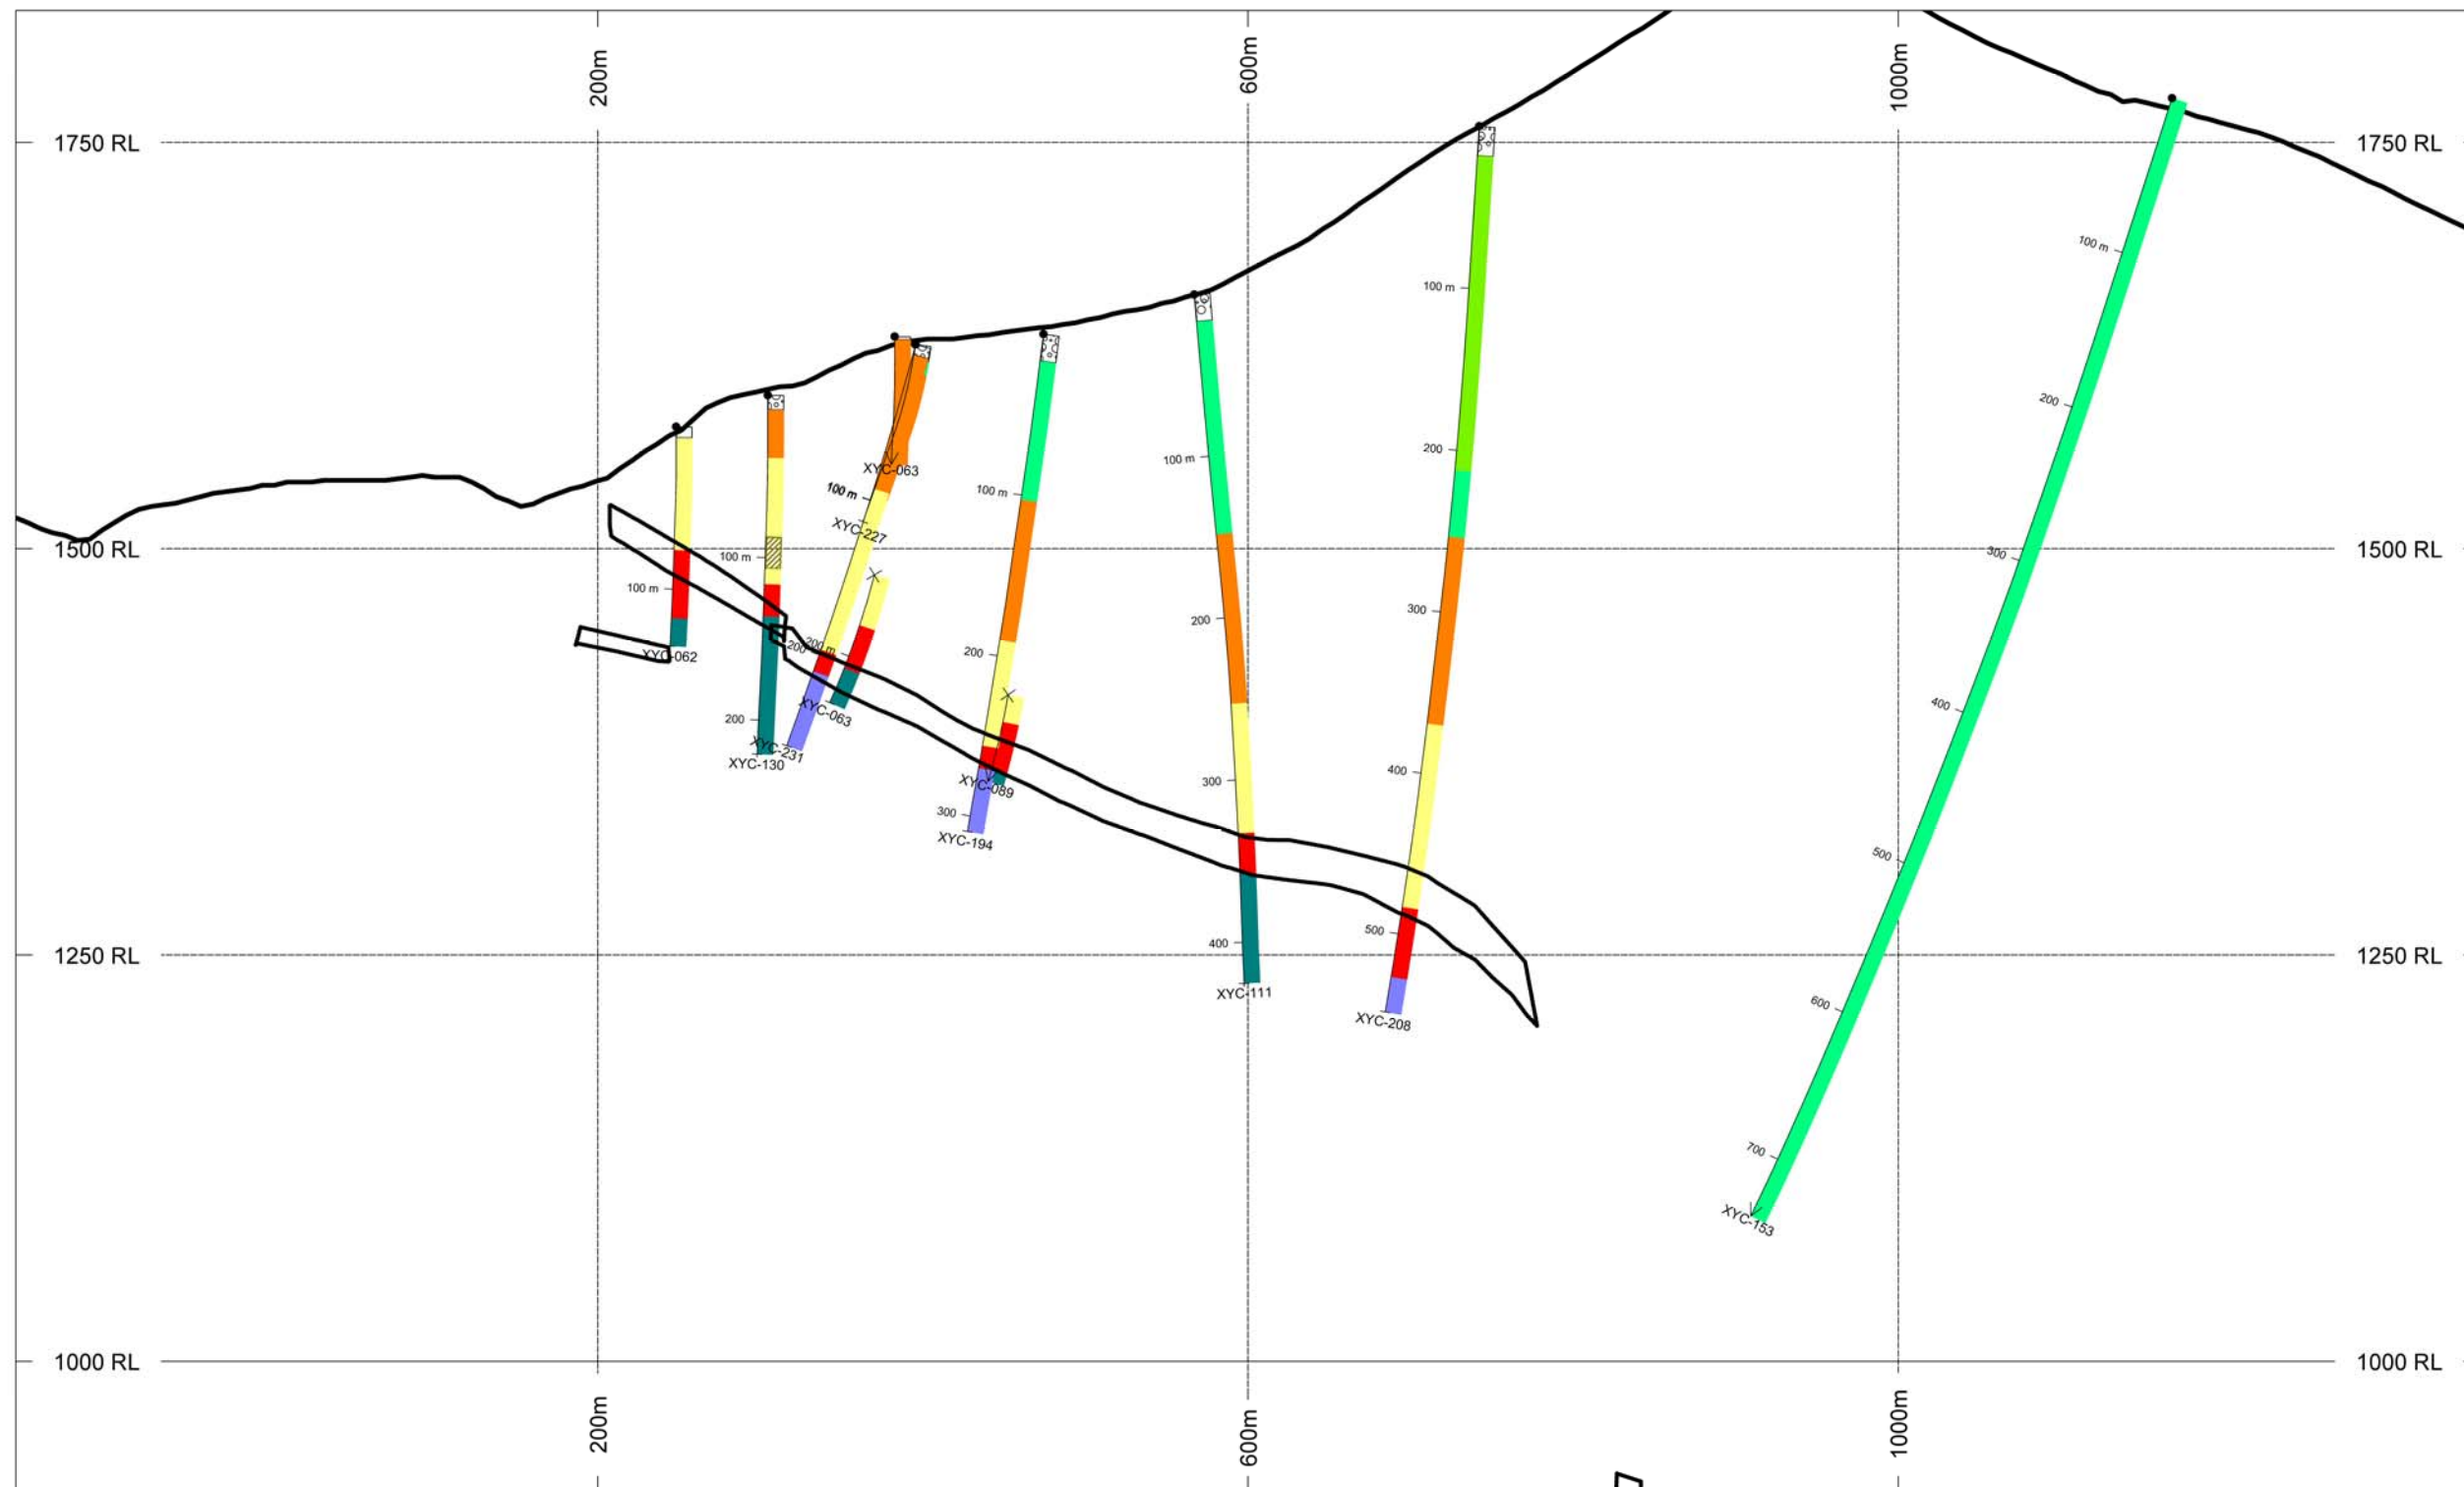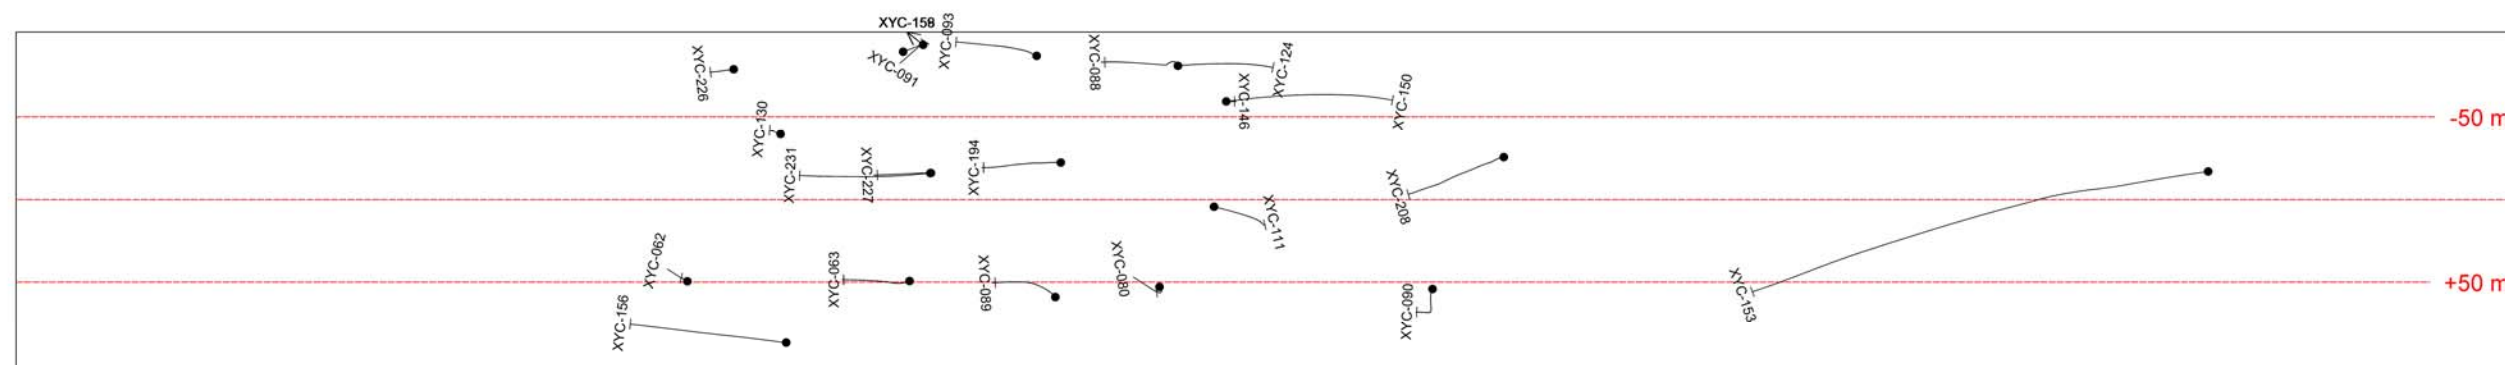

HOLES PLOTTED

TOTAL 10

XYC-062	XYC-063	XYC-089	XYC-111
XYC-130	XYC-153	XYC-194	XYC-208
XYC-227	XYC-231		





SELWYN CHIHONG
MINING LTD.

ROCK CODES	PAT	LABEL	DESCRIPTION
rocktype		FECR	Iron Creek Formation
		BSSM	Backside Siliceous Mudstone
		FLMD	Flaggy Mudstone
		USMS	Upper Siliceous Mudstone
		ACTM	Active Member
		LCMS	Lower Cherty Mudstone
		CCMS	Calcareous Mudstone
		PSMS	Pyritic Mudstone
		TRAN	Transition Formation
		CLST	Cambrian Limestone
		OVBR	Overburden
		FLT	Fault
		MDST	Undefined Mudstone

SECTION SPECS:

REF. PT. E, N	488779 m	6926628 m
EXTENTS	1516 m	911.9 m
SECTION TOP, BOT	1831 m	919.3 m
TOLERANCE +/-	50 m	


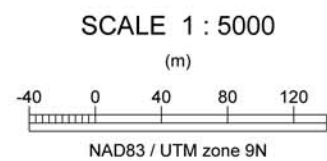


Selwyn Chihong Mining Ltd.

Selwyn Project, YT

Section L_02600N/0600E

XY Central Deposit

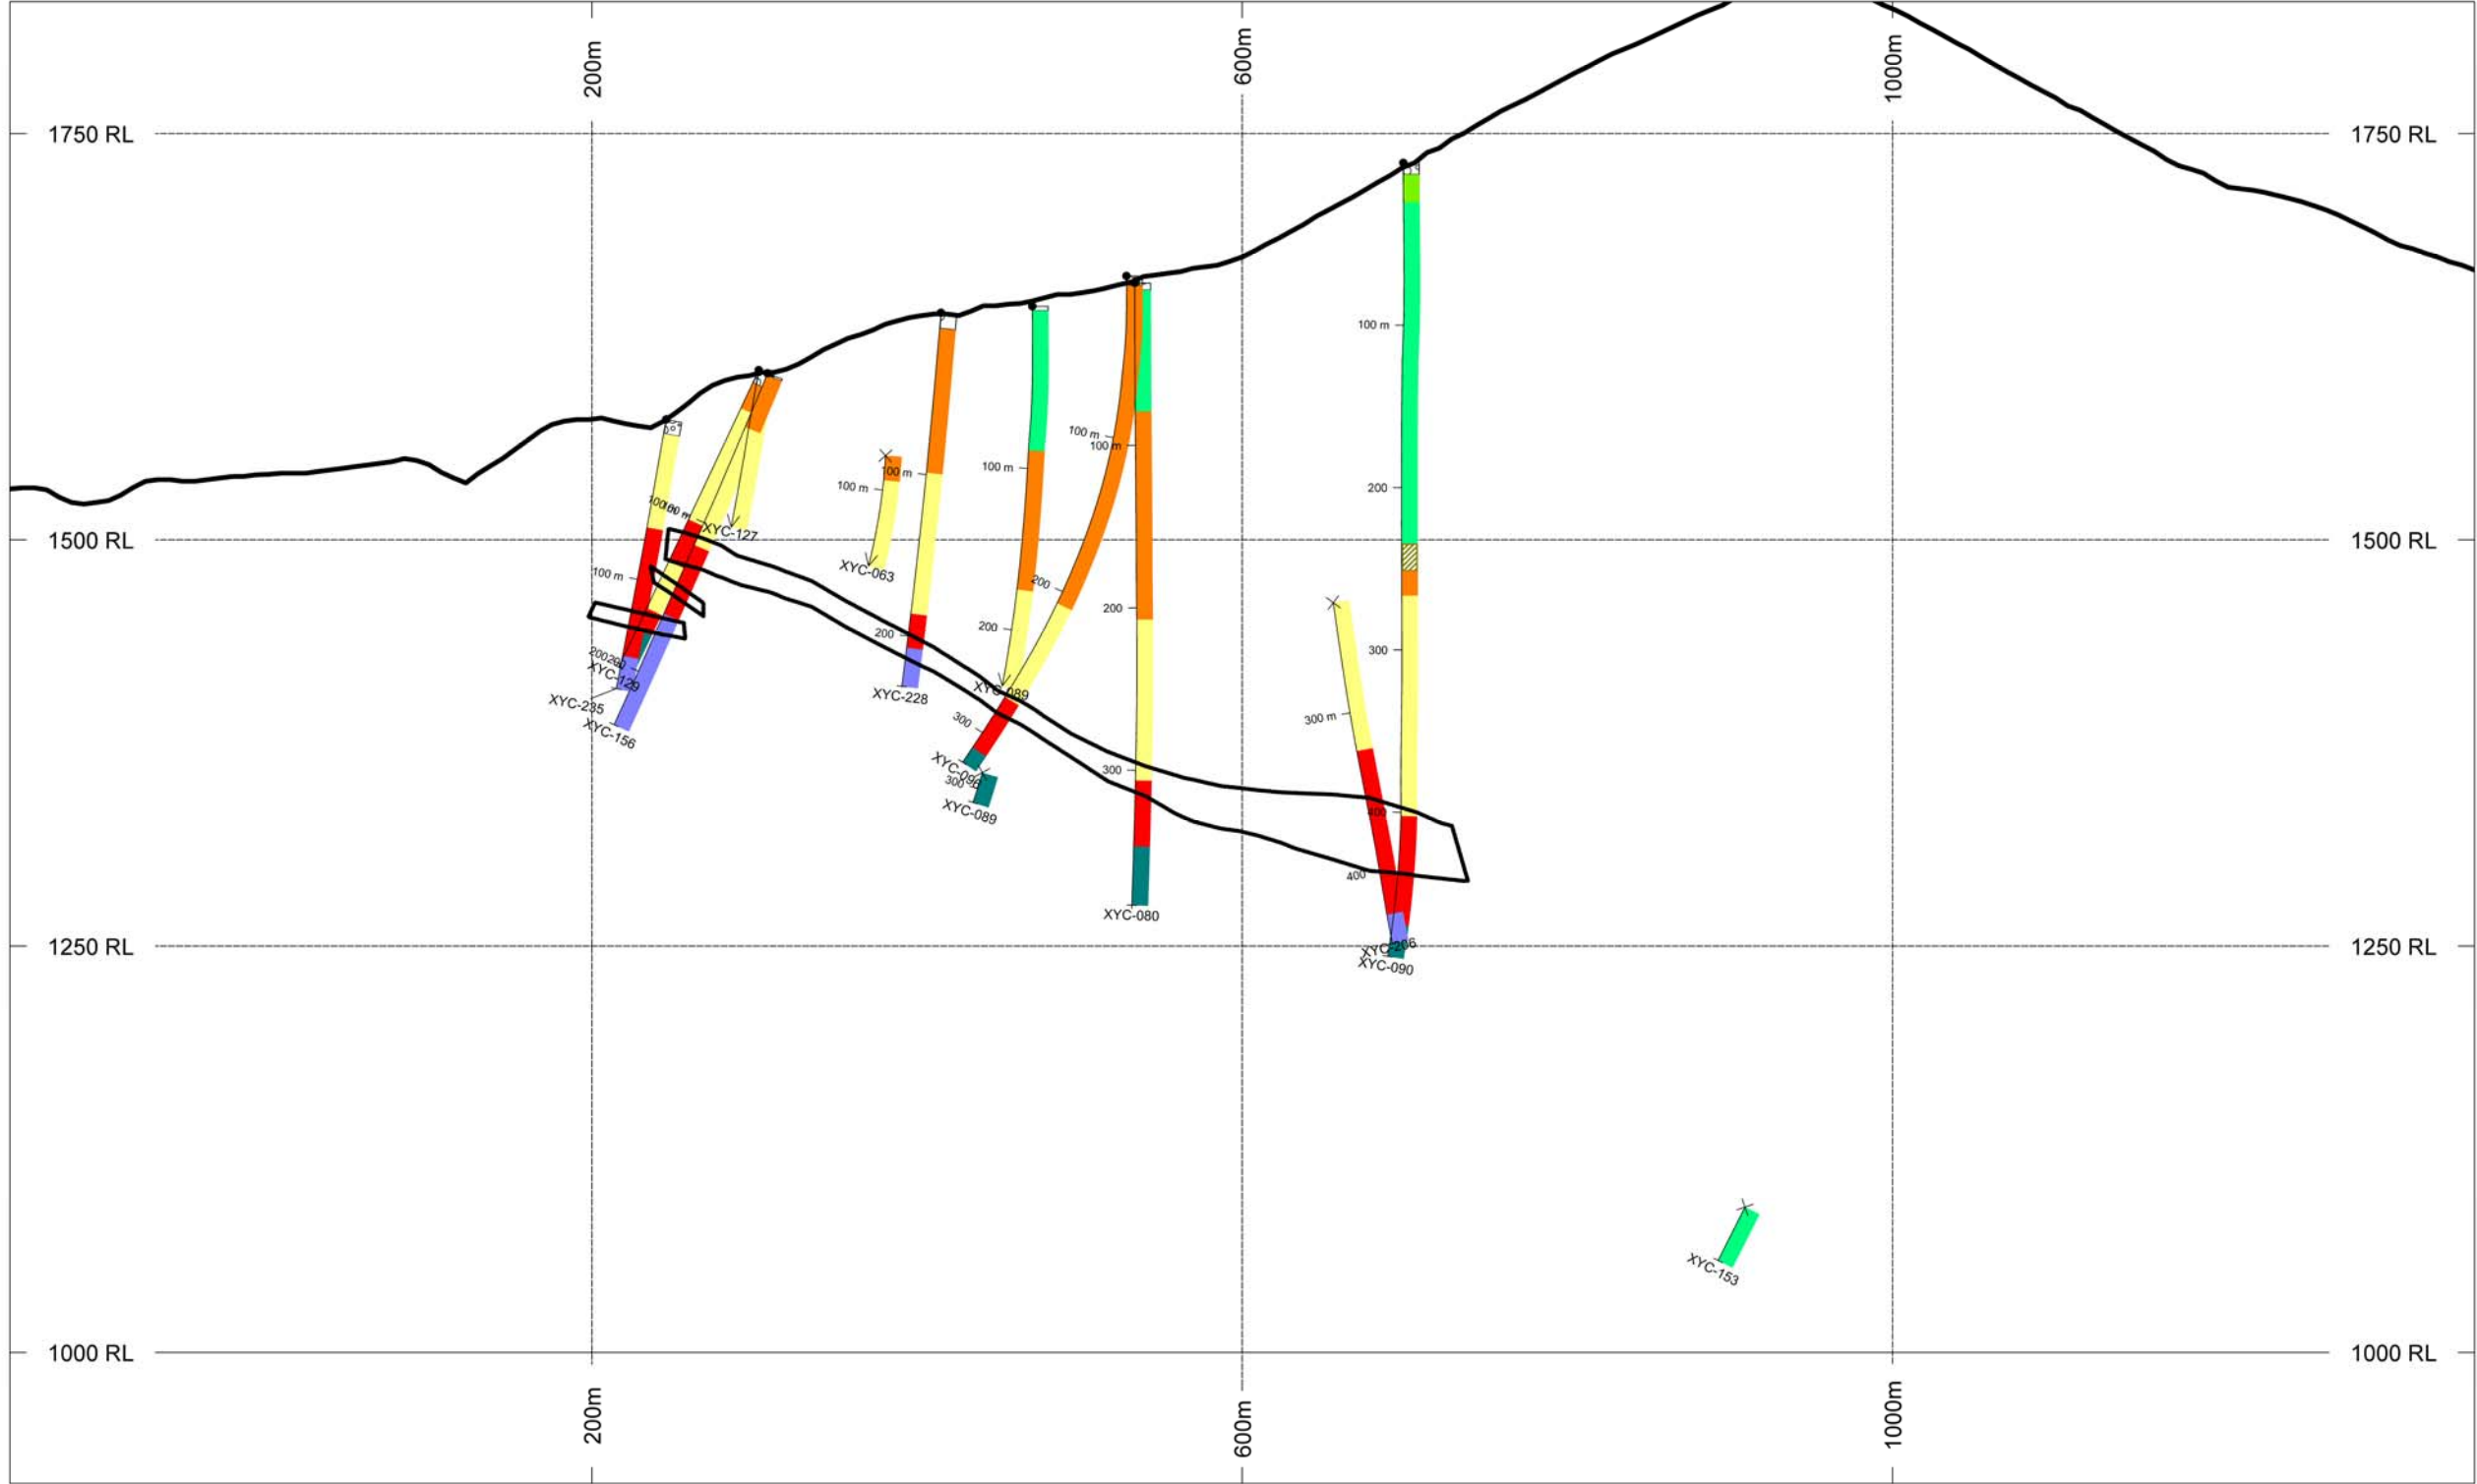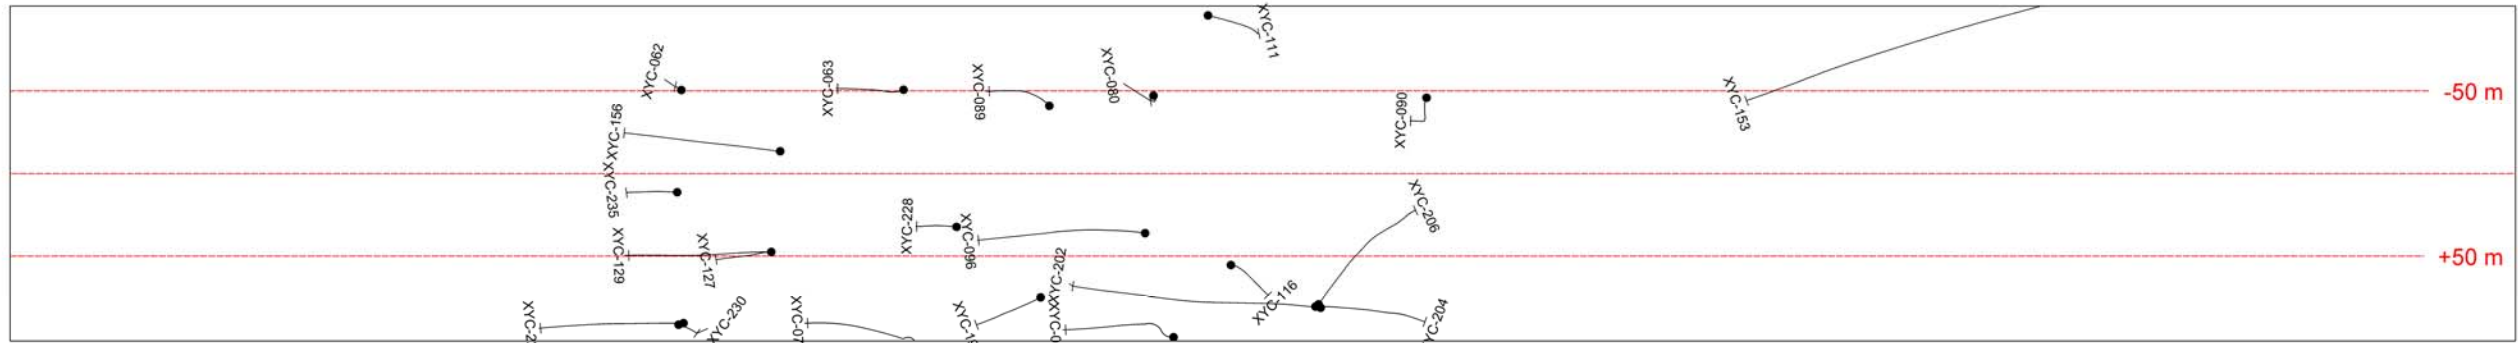

HOLES PLOTTED

TOTAL 12

XYC-063	XYC-080	XYC-089	XYC-090
XYC-096	XYC-127	XYC-129	XYC-153
XYC-156	XYC-206	XYC-228	XYC-235





SELWYN CHIHONG
MINING LTD.

ROCK CODES	PAT	LABEL	DESCRIPTION
rocktype			
		FECR	Iron Creek Formation
		BSSM	Backside Siliceous Mudstone
		FLMD	Flaggy Mudstone
		USMS	Upper Siliceous Mudstone
		ACTM	Active Member
		LCMS	Lower Cherty Mudstone
		CCMS	Calcareous Mudstone
		PSMS	Pyritic Mudstone
		TRAN	Transition Formation
		CLST	Cambrian Limestone
		OVBR	Overburden
		FLT	Fault
		MDST	Undefined Mudstone

SECTION SPECS:

REF. PT. E, N	488866 m	6926578 m
EXTENTS	1516 m	911.9 m
SECTION TOP, BOT	1831 m	919.3 m
TOLERANCE +/-	50 m	


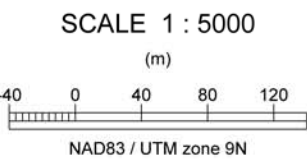


Selwyn Chihong Mining Ltd.

Selwyn Project, YT

Section L_02500N/0600E

XY Central Deposit

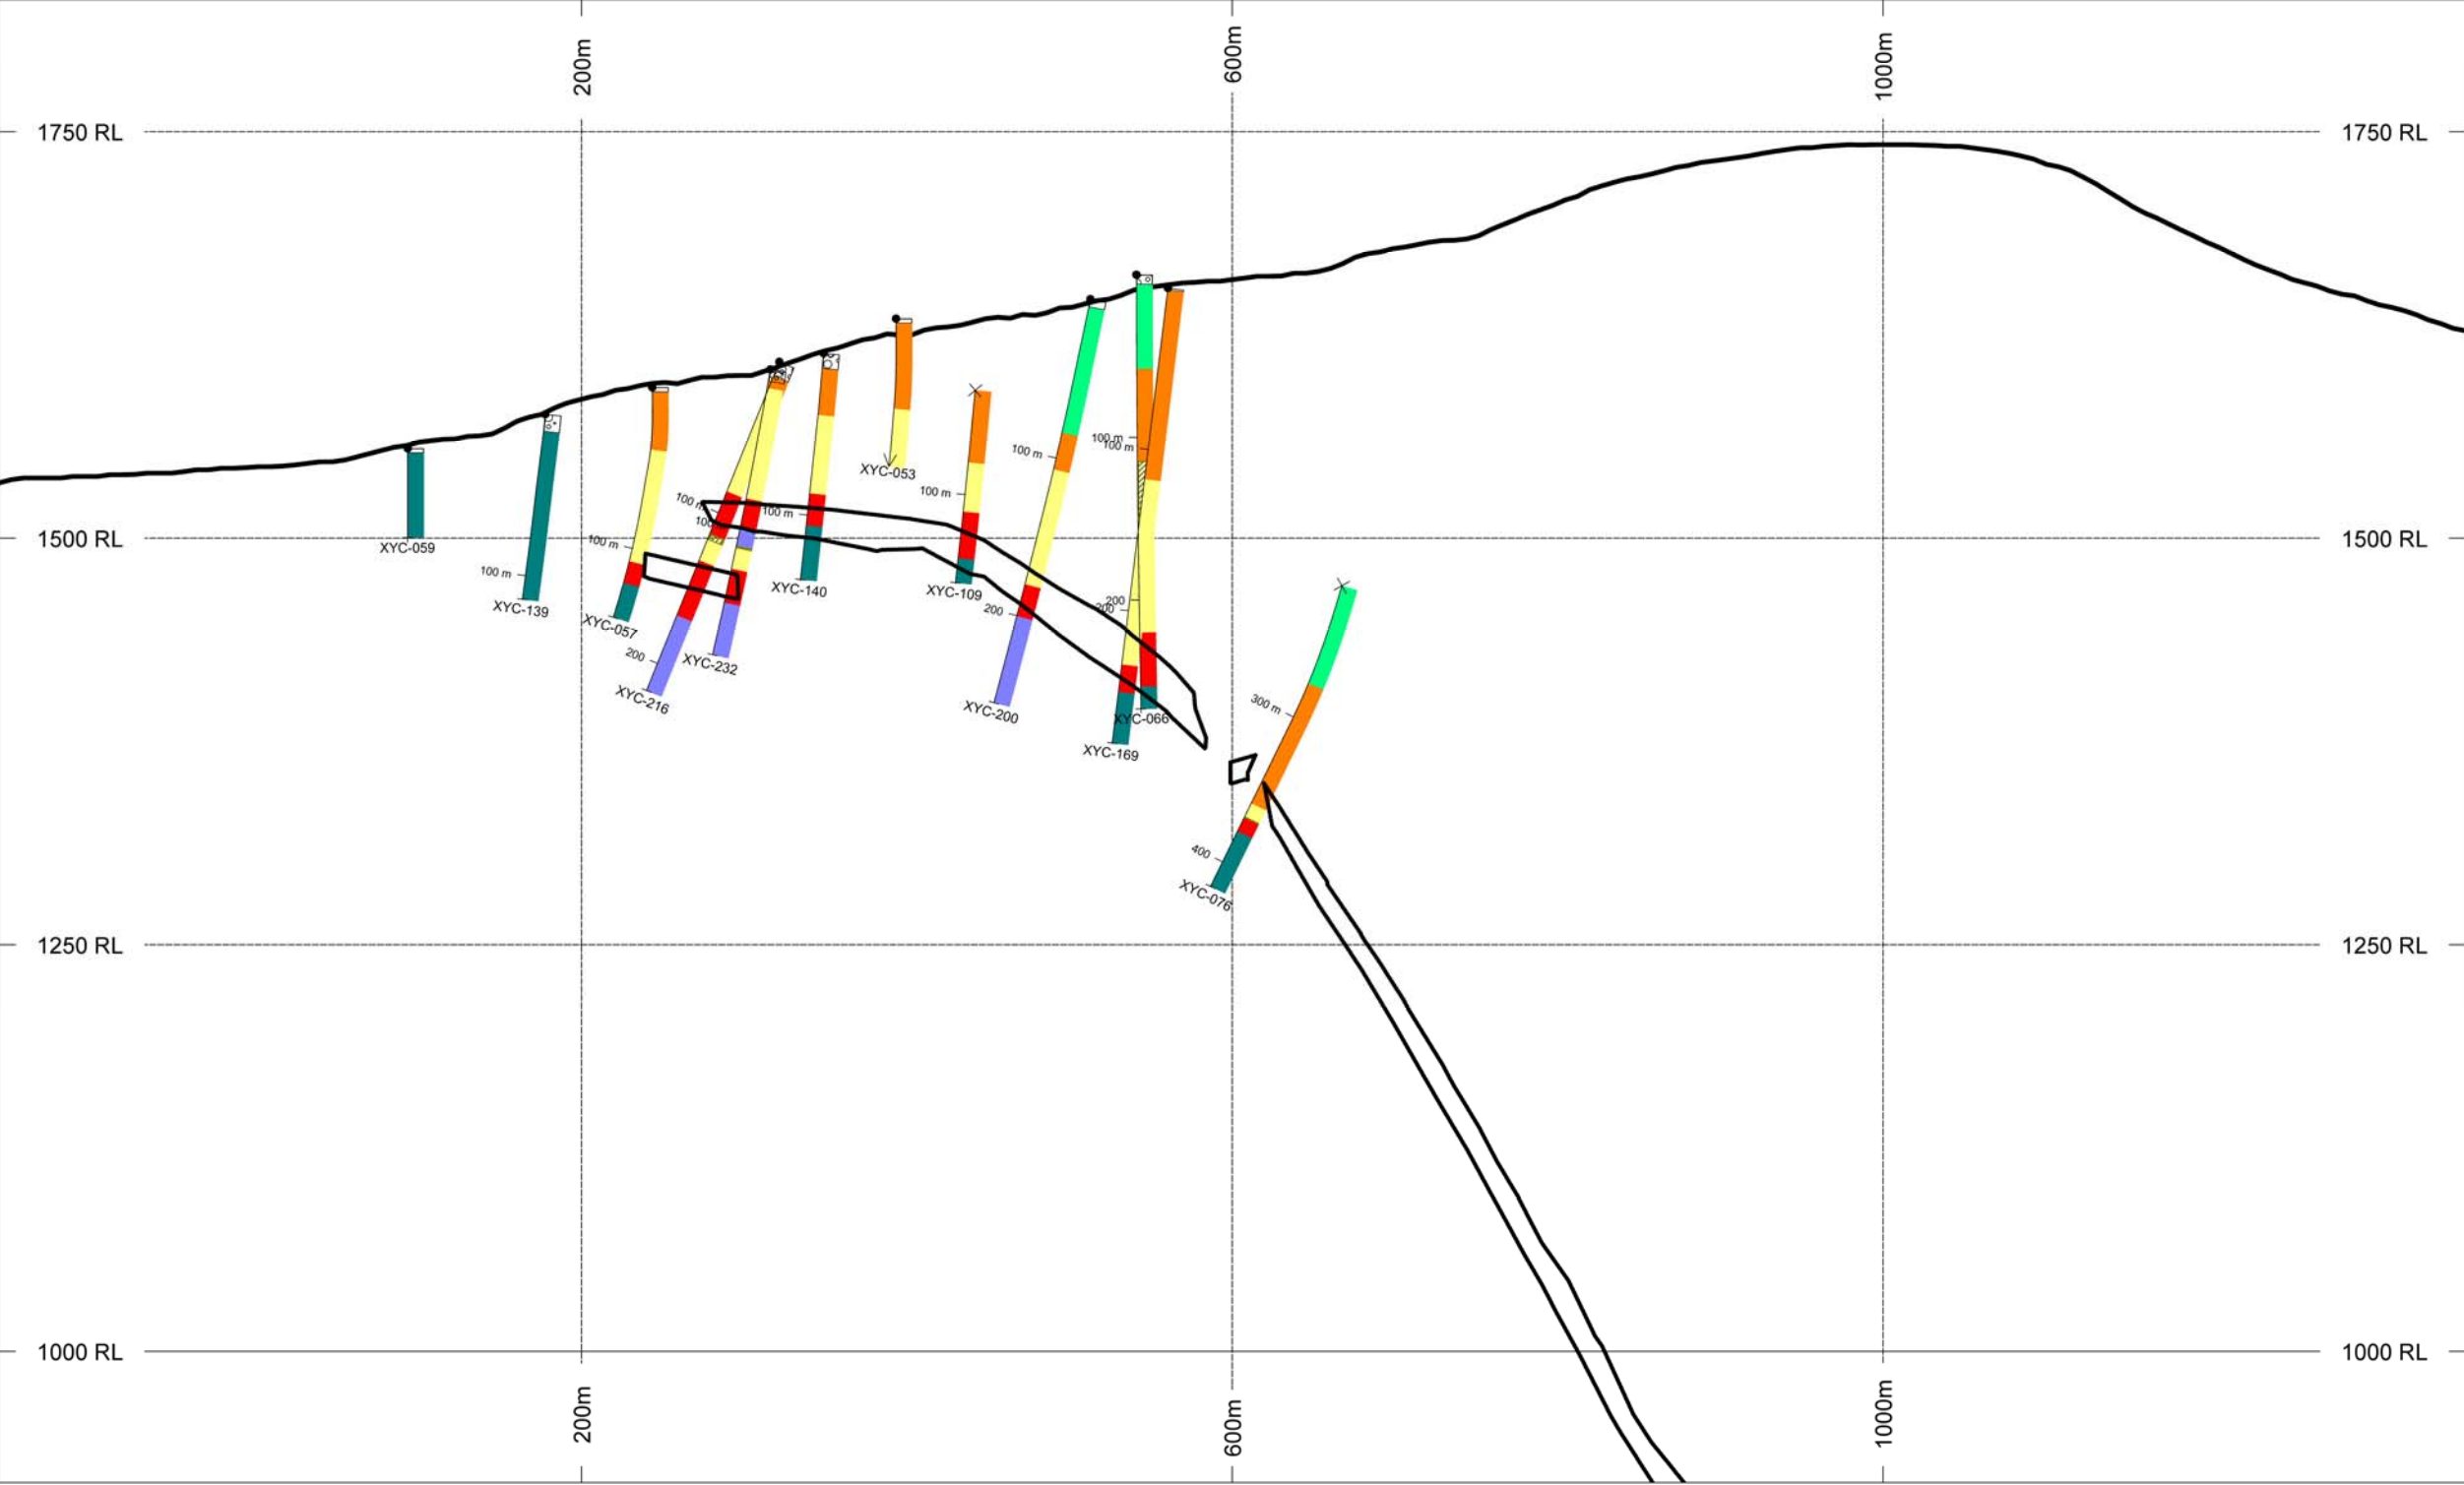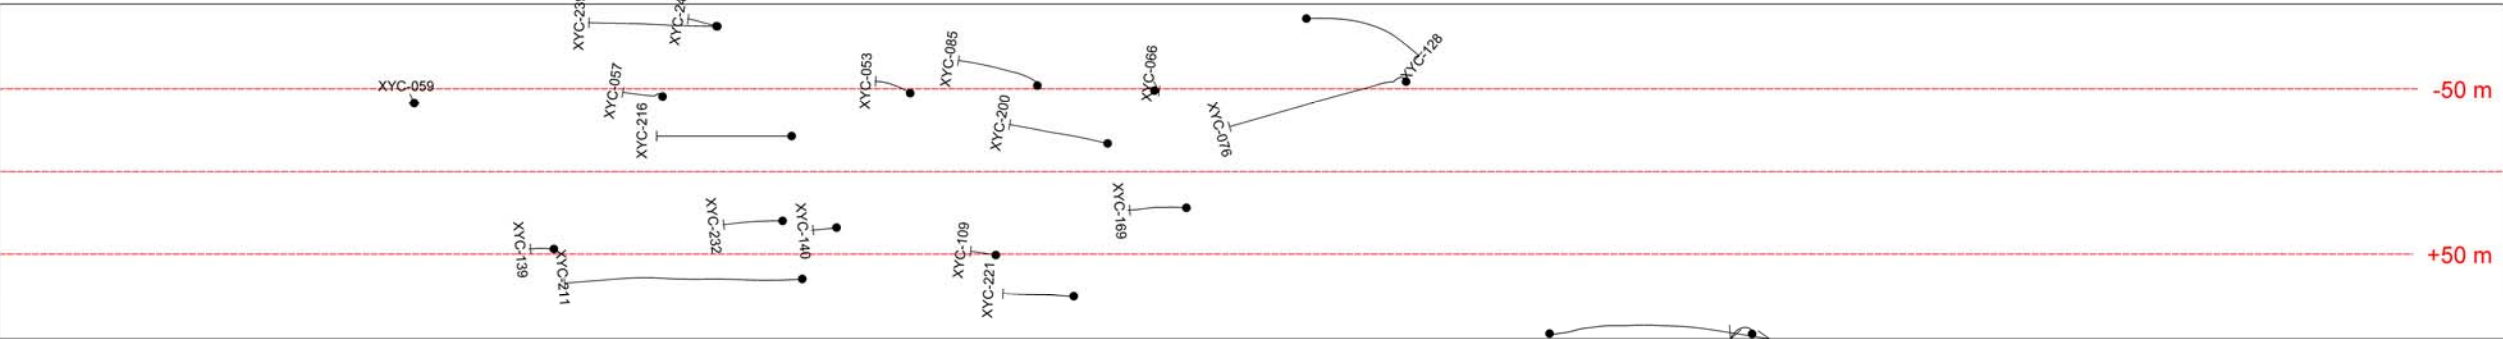

HOLES PLOTTED

TOTAL 12


XYC-053	XYC-057	XYC-059	XYC-066
XYC-076	XYC-109	XYC-139	XYC-140
XYC-169	XYC-200	XYC-216	XYC-232





ROCK CODES rocktype	PAT	LABEL	DESCRIPTION
		BSSM	Backside Siliceous Mudstone
		FLMD	Flaggy Mudstone
		USMS	Upper Siliceous Mudstone
		ACTM	Active Member
		LCMS	Lower Cherty Mudstone
		CCMS	Calcareous Mudstone
		PSMS	Pyritic Mudstone
		TRAN	Transition Formation
		CLST	Cambrian Limestone
		OVBR	Overburden
		FLT	Fault
		MDST	Undefined Mudstone

SECTION SPECS:

REF. PT. E, N	489126 m	6926428 m
EXTENTS	1516 m	911.9 m
SECTION TOP, BOT	1831 m	919.3 m
TOLERANCE +/-	50 m	

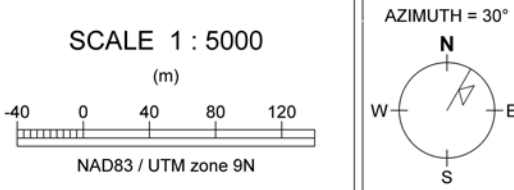

Selwyn Chihong Mining Ltd.
Selwyn Project, YT
Section L_02200N/0600E
XY Central Deposit

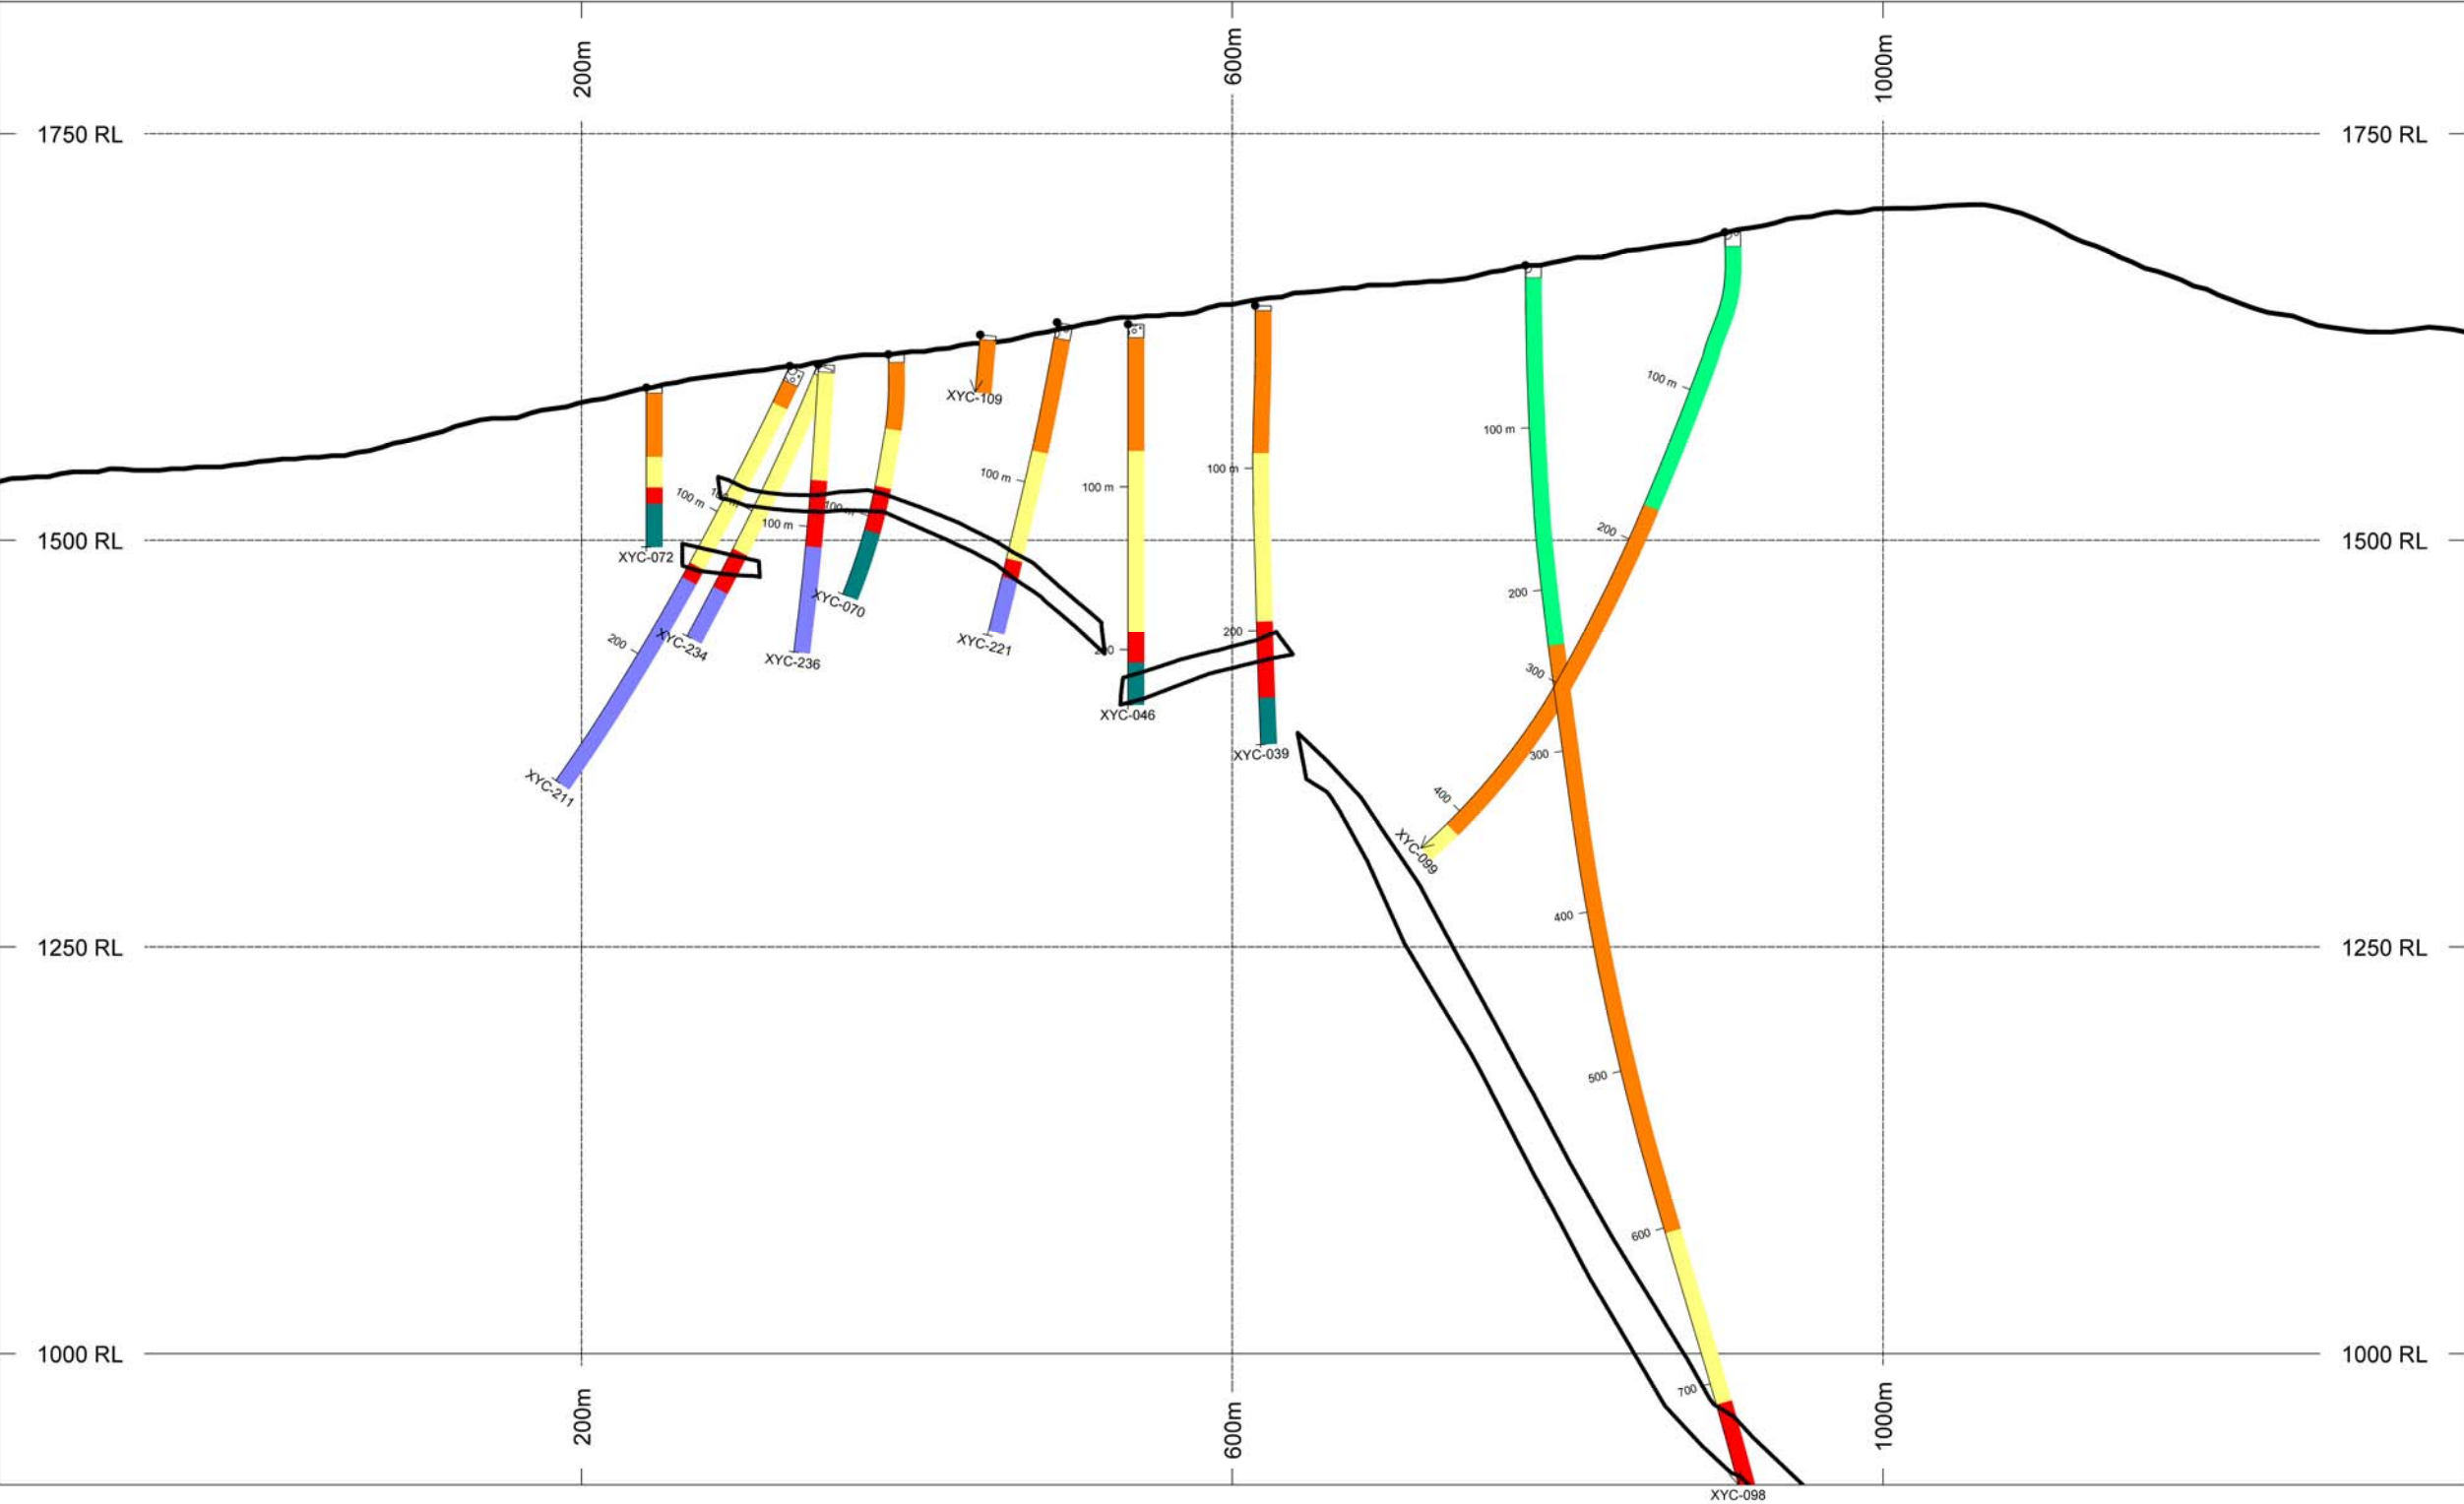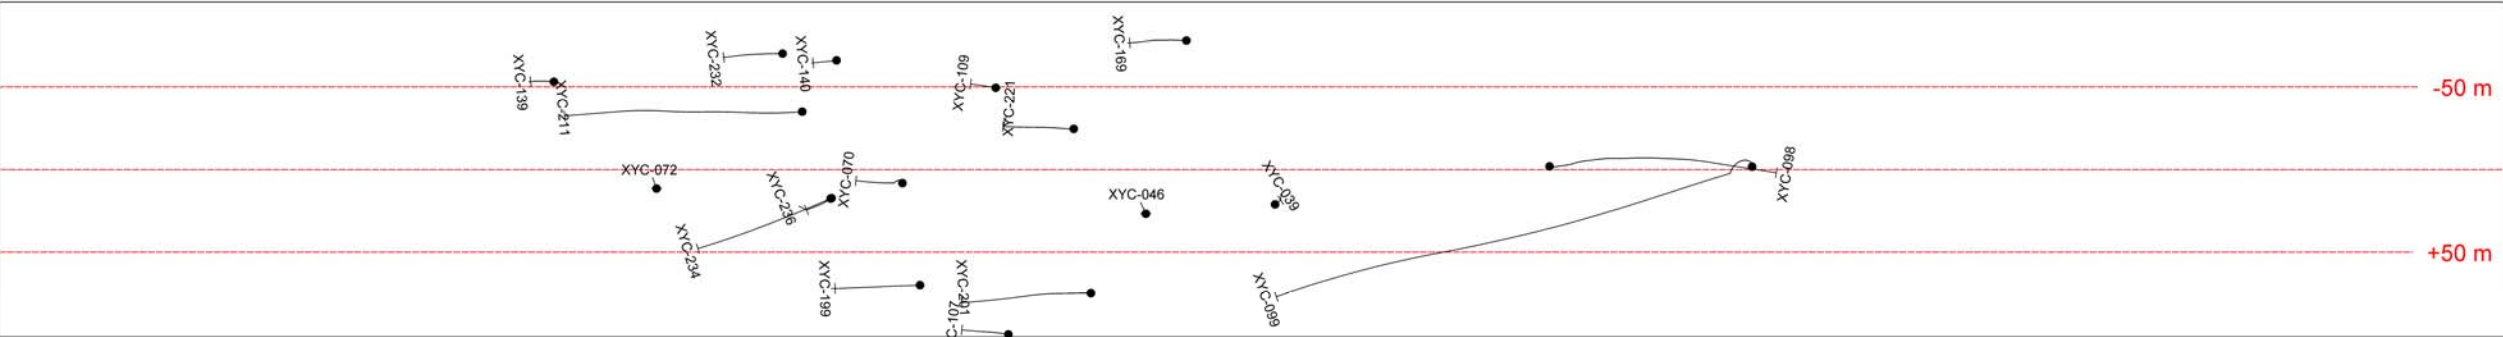

HOLES PLOTTED

TOTAL 11



XYC-039	XYC-046	XYC-070	XYC-072
XYC-098	XYC-099	XYC-109	XYC-211
XYC-221	XYC-234	XYC-236	





ROCK CODES rocktype	PAT	LABEL	DESCRIPTION
		BSSM	Backside Siliceous Mudstone
		FLMD	Flaggy Mudstone
		USMS	Upper Siliceous Mudstone
		ACTM	Active Member
		LCMS	Lower Cherty Mudstone
		CCMS	Calcareous Mudstone
		PSMS	Pyritic Mudstone
		TRAN	Transition Formation
		CLST	Cambrian Limestone
		OVBR	Overburden
		FLT	Fault
		MDST	Undefined Mudstone

SECTION SPECS:

REF. PT. E, N	489212 m	6926378 m
EXTENTS	1516 m	911.9 m
SECTION TOP, BOT	1831 m	919.3 m
TOLERANCE +/-	50 m	

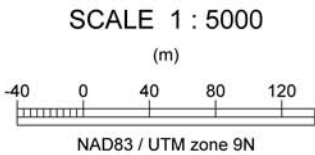

Selwyn Chihong Mining Ltd.
Selwyn Project, YT
Section L_02100N/0600E
XY Central Deposit

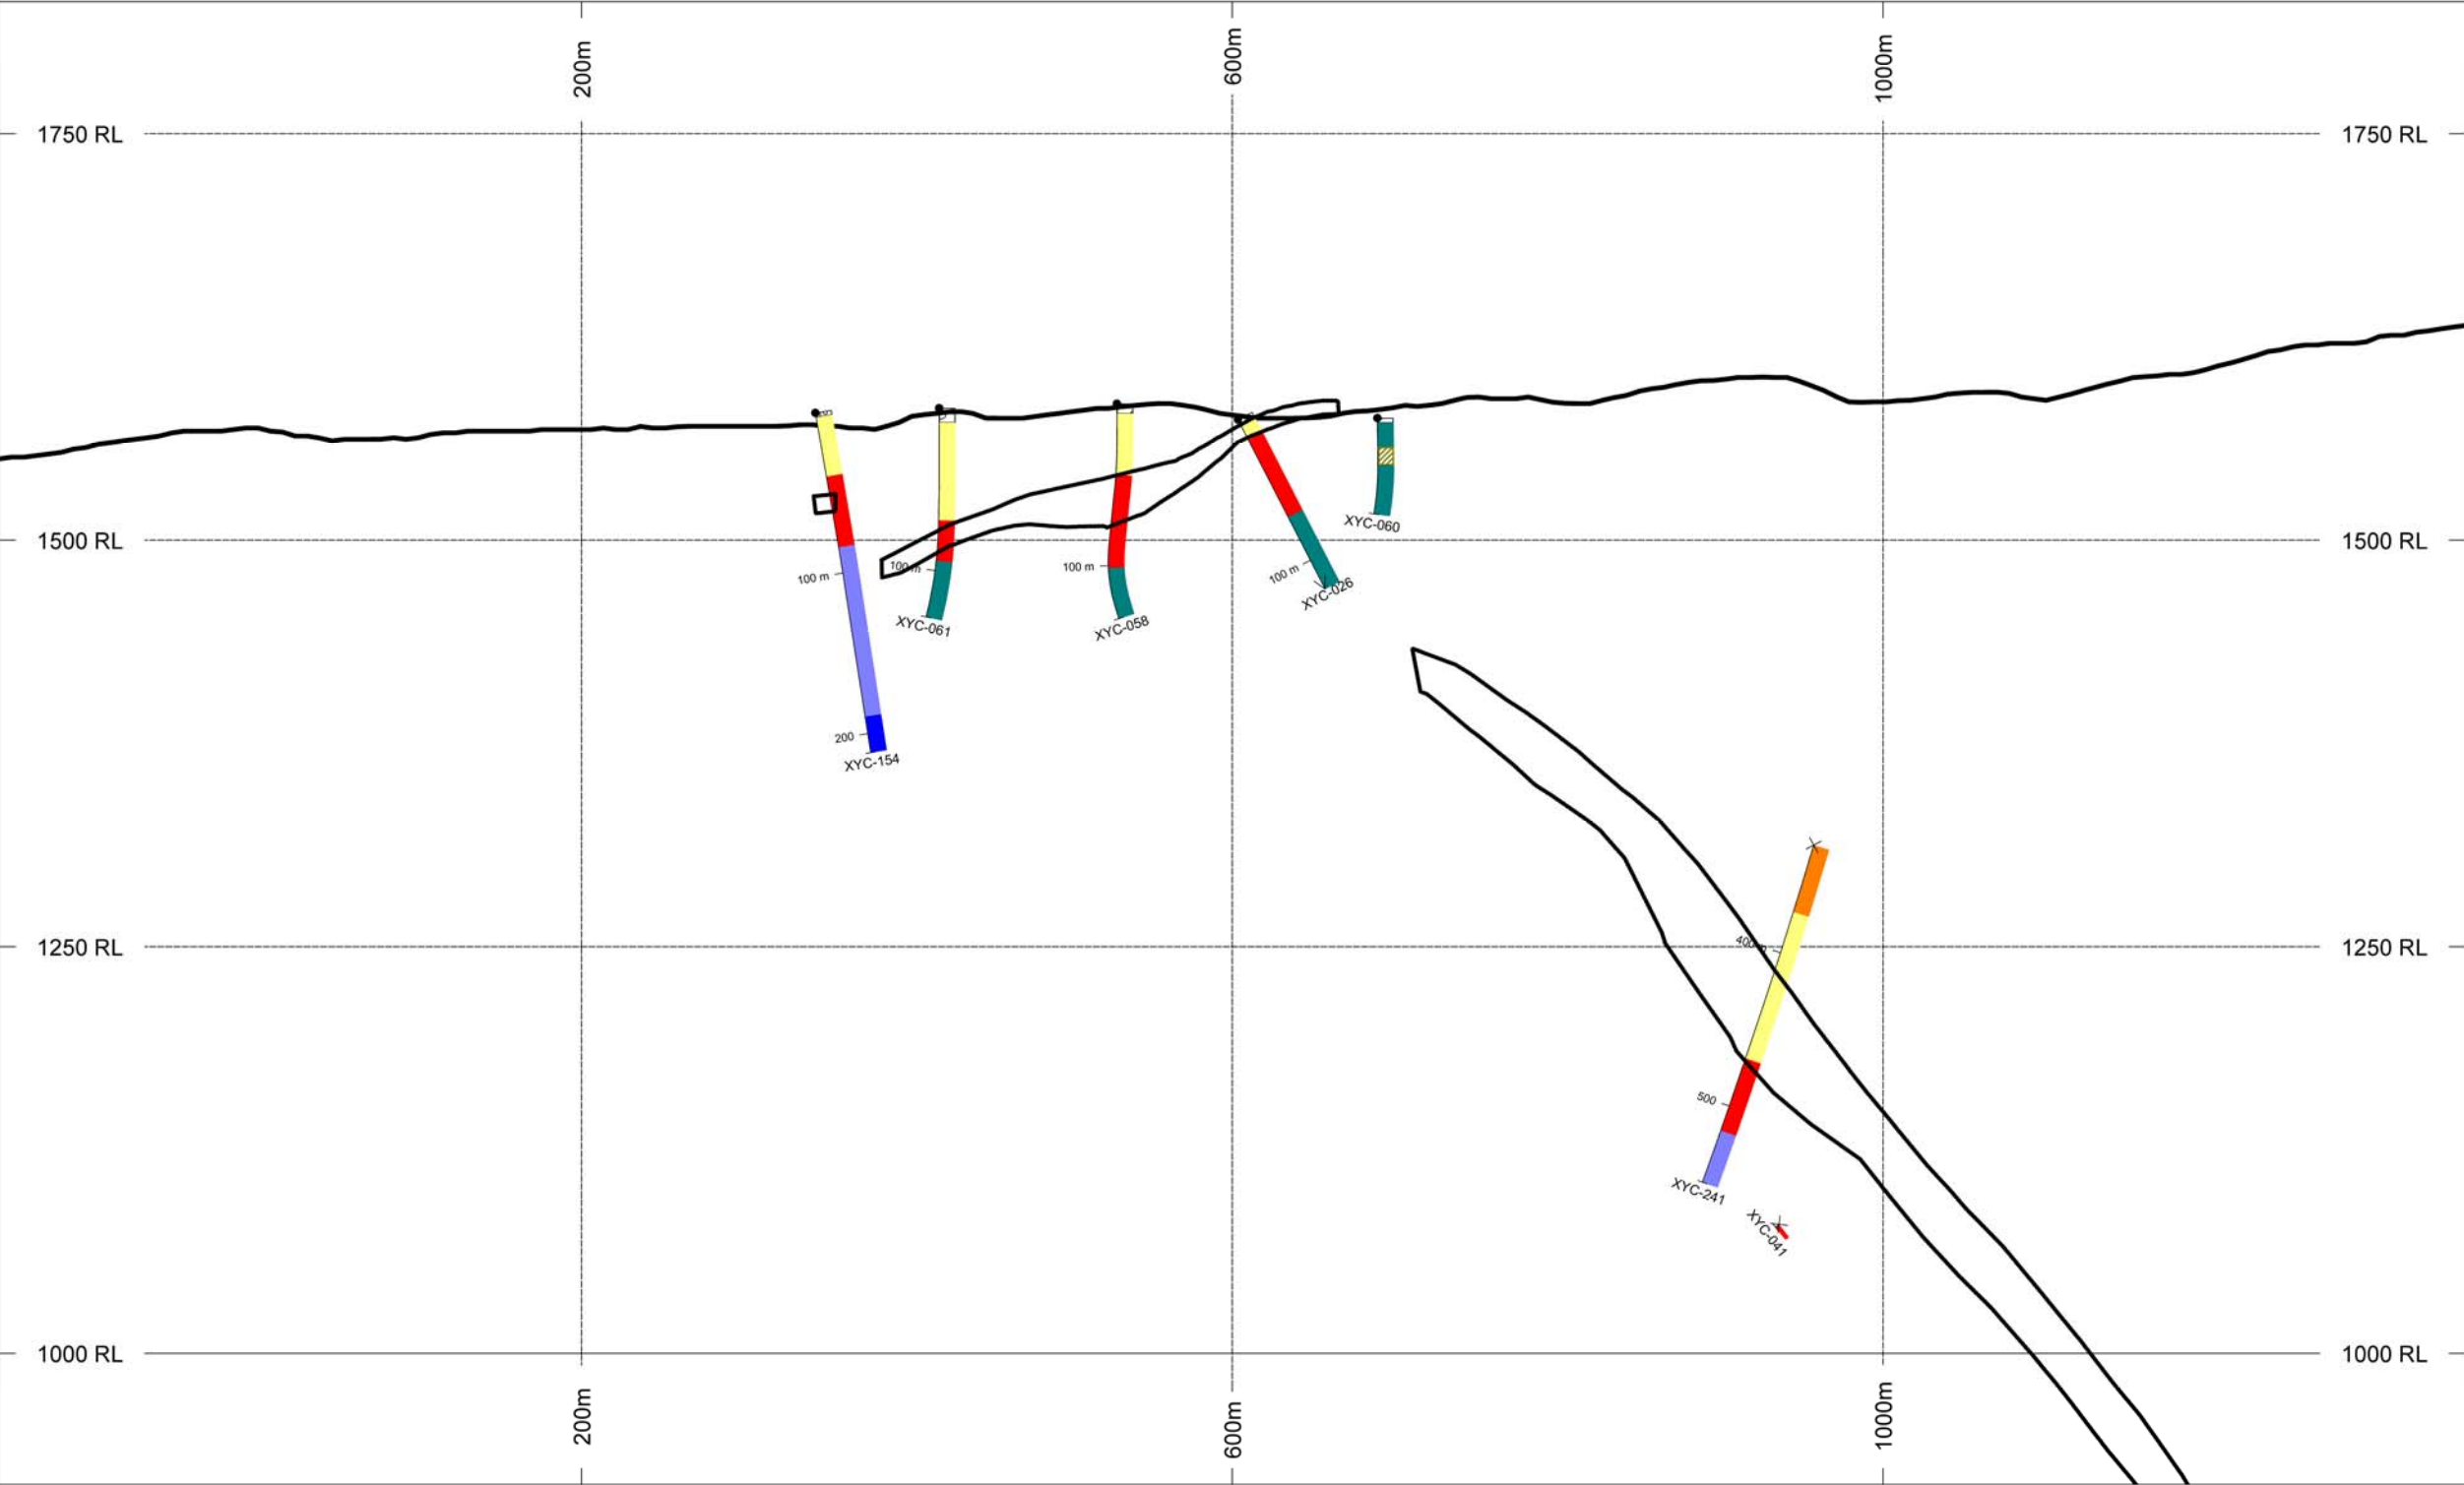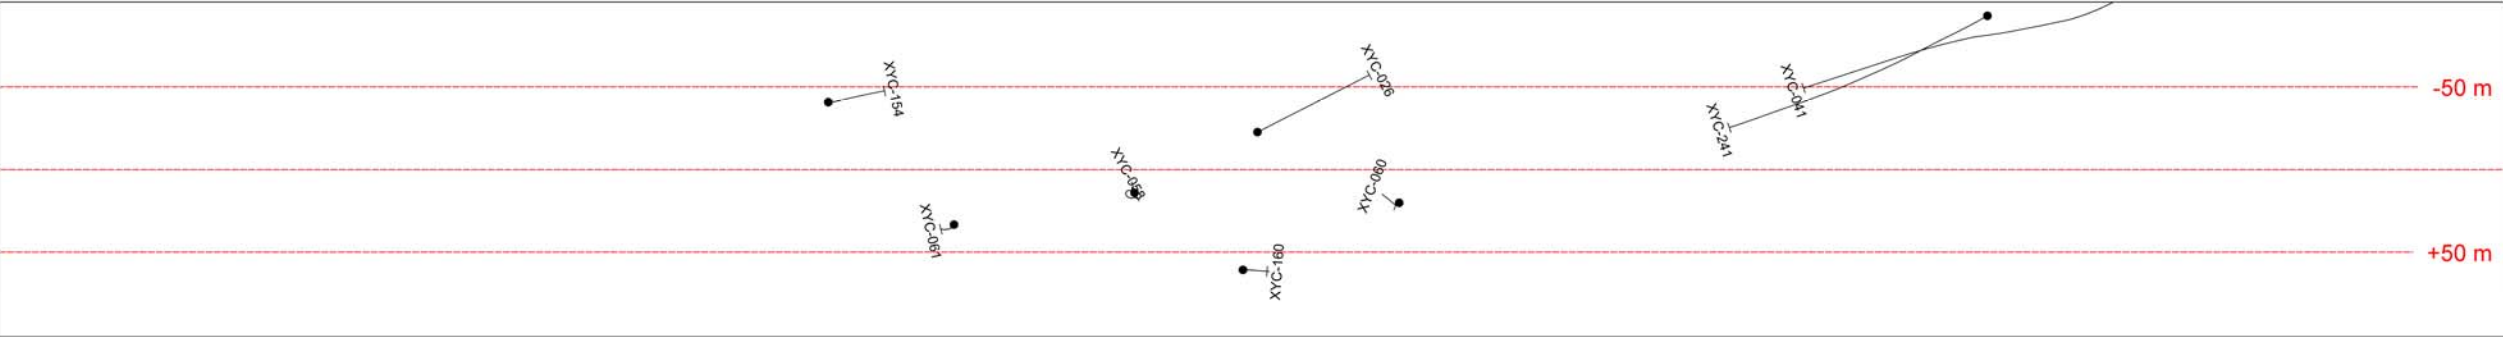

HOLES PLOTTED

TOTAL 7

XYC-026	XYC-041	XYC-058	XYC-060
XYC-061	XYC-154	XYC-241	




SELWYN CHIHONG
MINING LTD.



ROCK CODES	PAT	LABEL	DESCRIPTION
rocktype			
		BSSM	Backside Siliceous Mudstone
		FLMD	Flaggy Mudstone
		USMS	Upper Siliceous Mudstone
		ACTM	Active Member
		LCMS	Lower Cherty Mudstone
		CCMS	Calcareous Mudstone
		PSMS	Pyritic Mudstone
		TRAN	Transition Formation
		CLST	Cambrian Limestone
		OVBR	Overburden
		FLT	Fault
		MDST	Undefined Mudstone

SECTION SPECS:

REF. PT. E, N	489472 m	6926228 m
EXTENTS	1516 m	911.9 m
SECTION TOP, BOT	1831 m	919.3 m
TOLERANCE +/-	50 m	

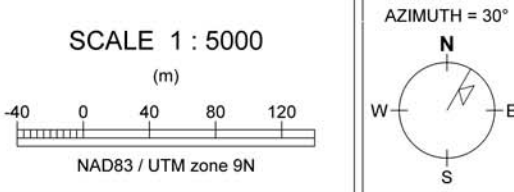

Selwyn Chihong Mining Ltd.
Selwyn Project, YT
Section L_01800N/0600E
XY Central Deposit

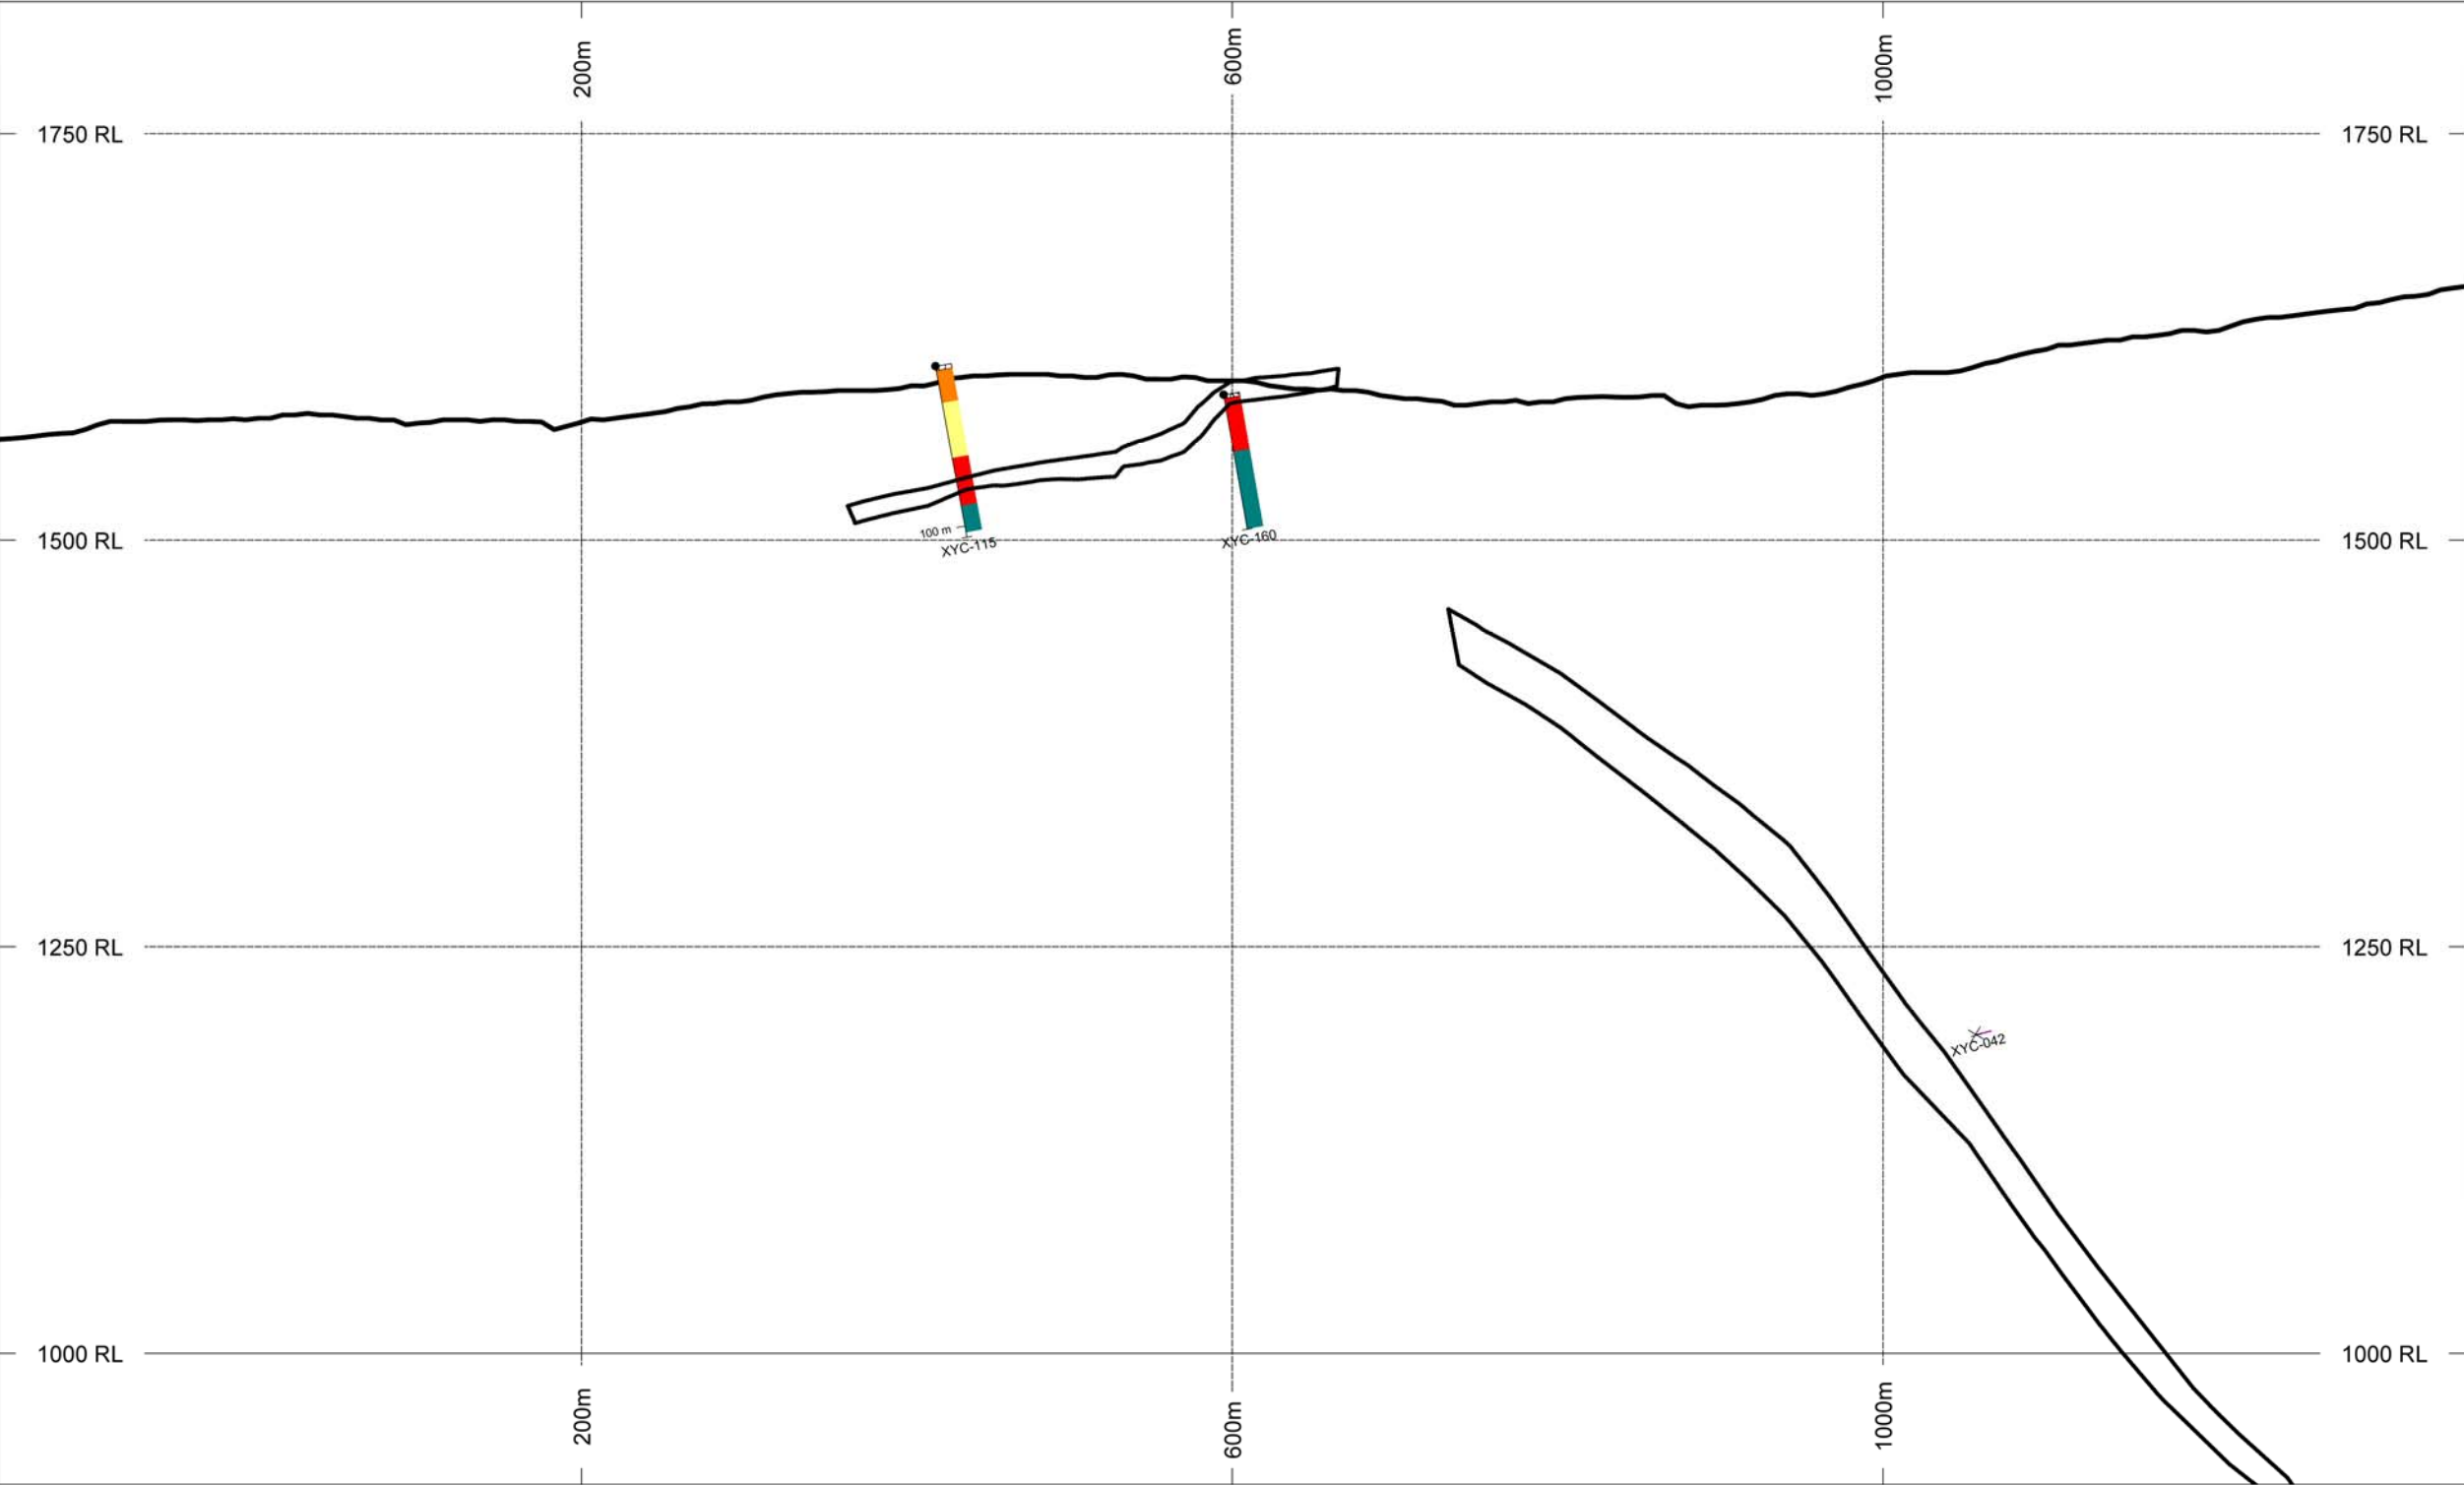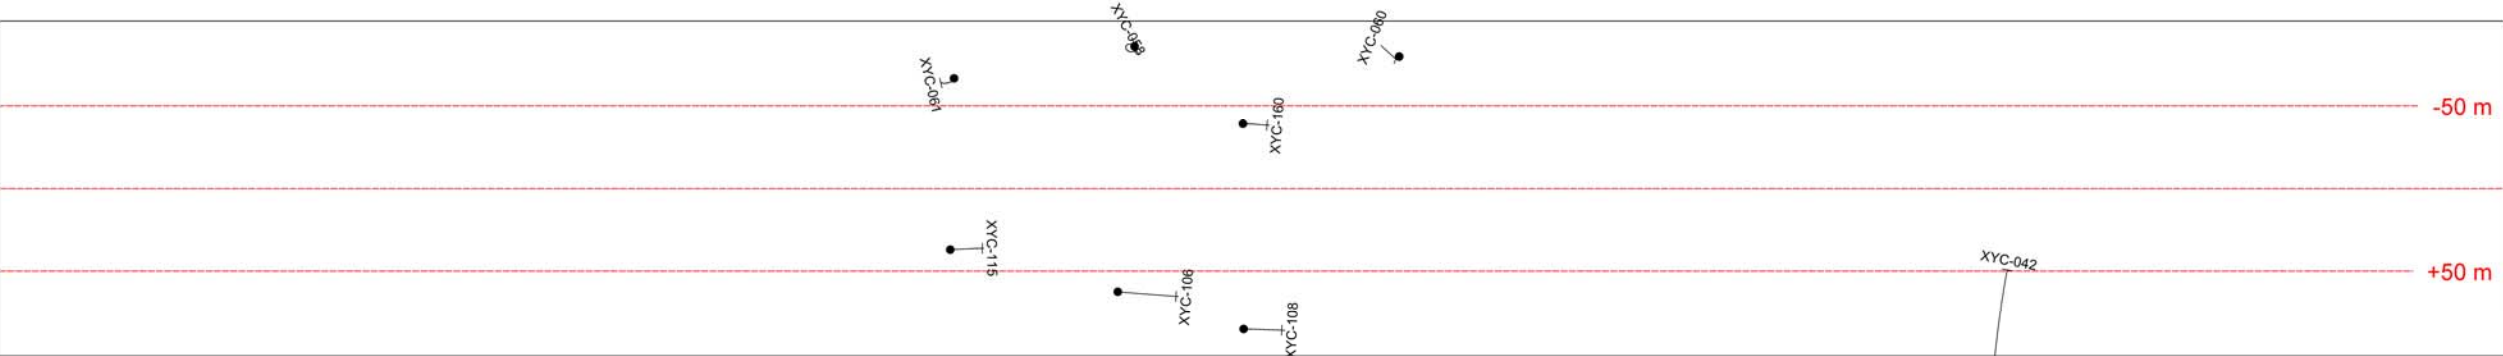

HOLES PLOTTED

TOTAL 3


XYC-042 XYC-115 XYC-160





ROCK CODES	PAT	LABEL	DESCRIPTION
rocktype		BSSM	Backside Siliceous Mudstone
		FLMD	Flaggy Mudstone
		USMS	Upper Siliceous Mudstone
		ACTM	Active Member
		LCMS	Lower Cherty Mudstone
		CCMS	Calcareous Mudstone
		PSMS	Pyritic Mudstone
		TRAN	Transition Formation
		CLST	Cambrian Limestone
		OVBR	Overburden
		FLT	Fault
		MDST	Undefined Mudstone

SECTION SPECS:

REF. PT. E, N	489559 m	6926178 m
EXTENTS	1516 m	911.9 m
SECTION TOP, BOT	1831 m	919.3 m
TOLERANCE +/-	50 m	

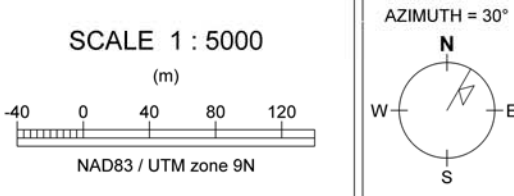

Selwyn Chihong Mining Ltd.
Selwyn Project, YT
Section L_01700N/0600E
XY Central Deposit

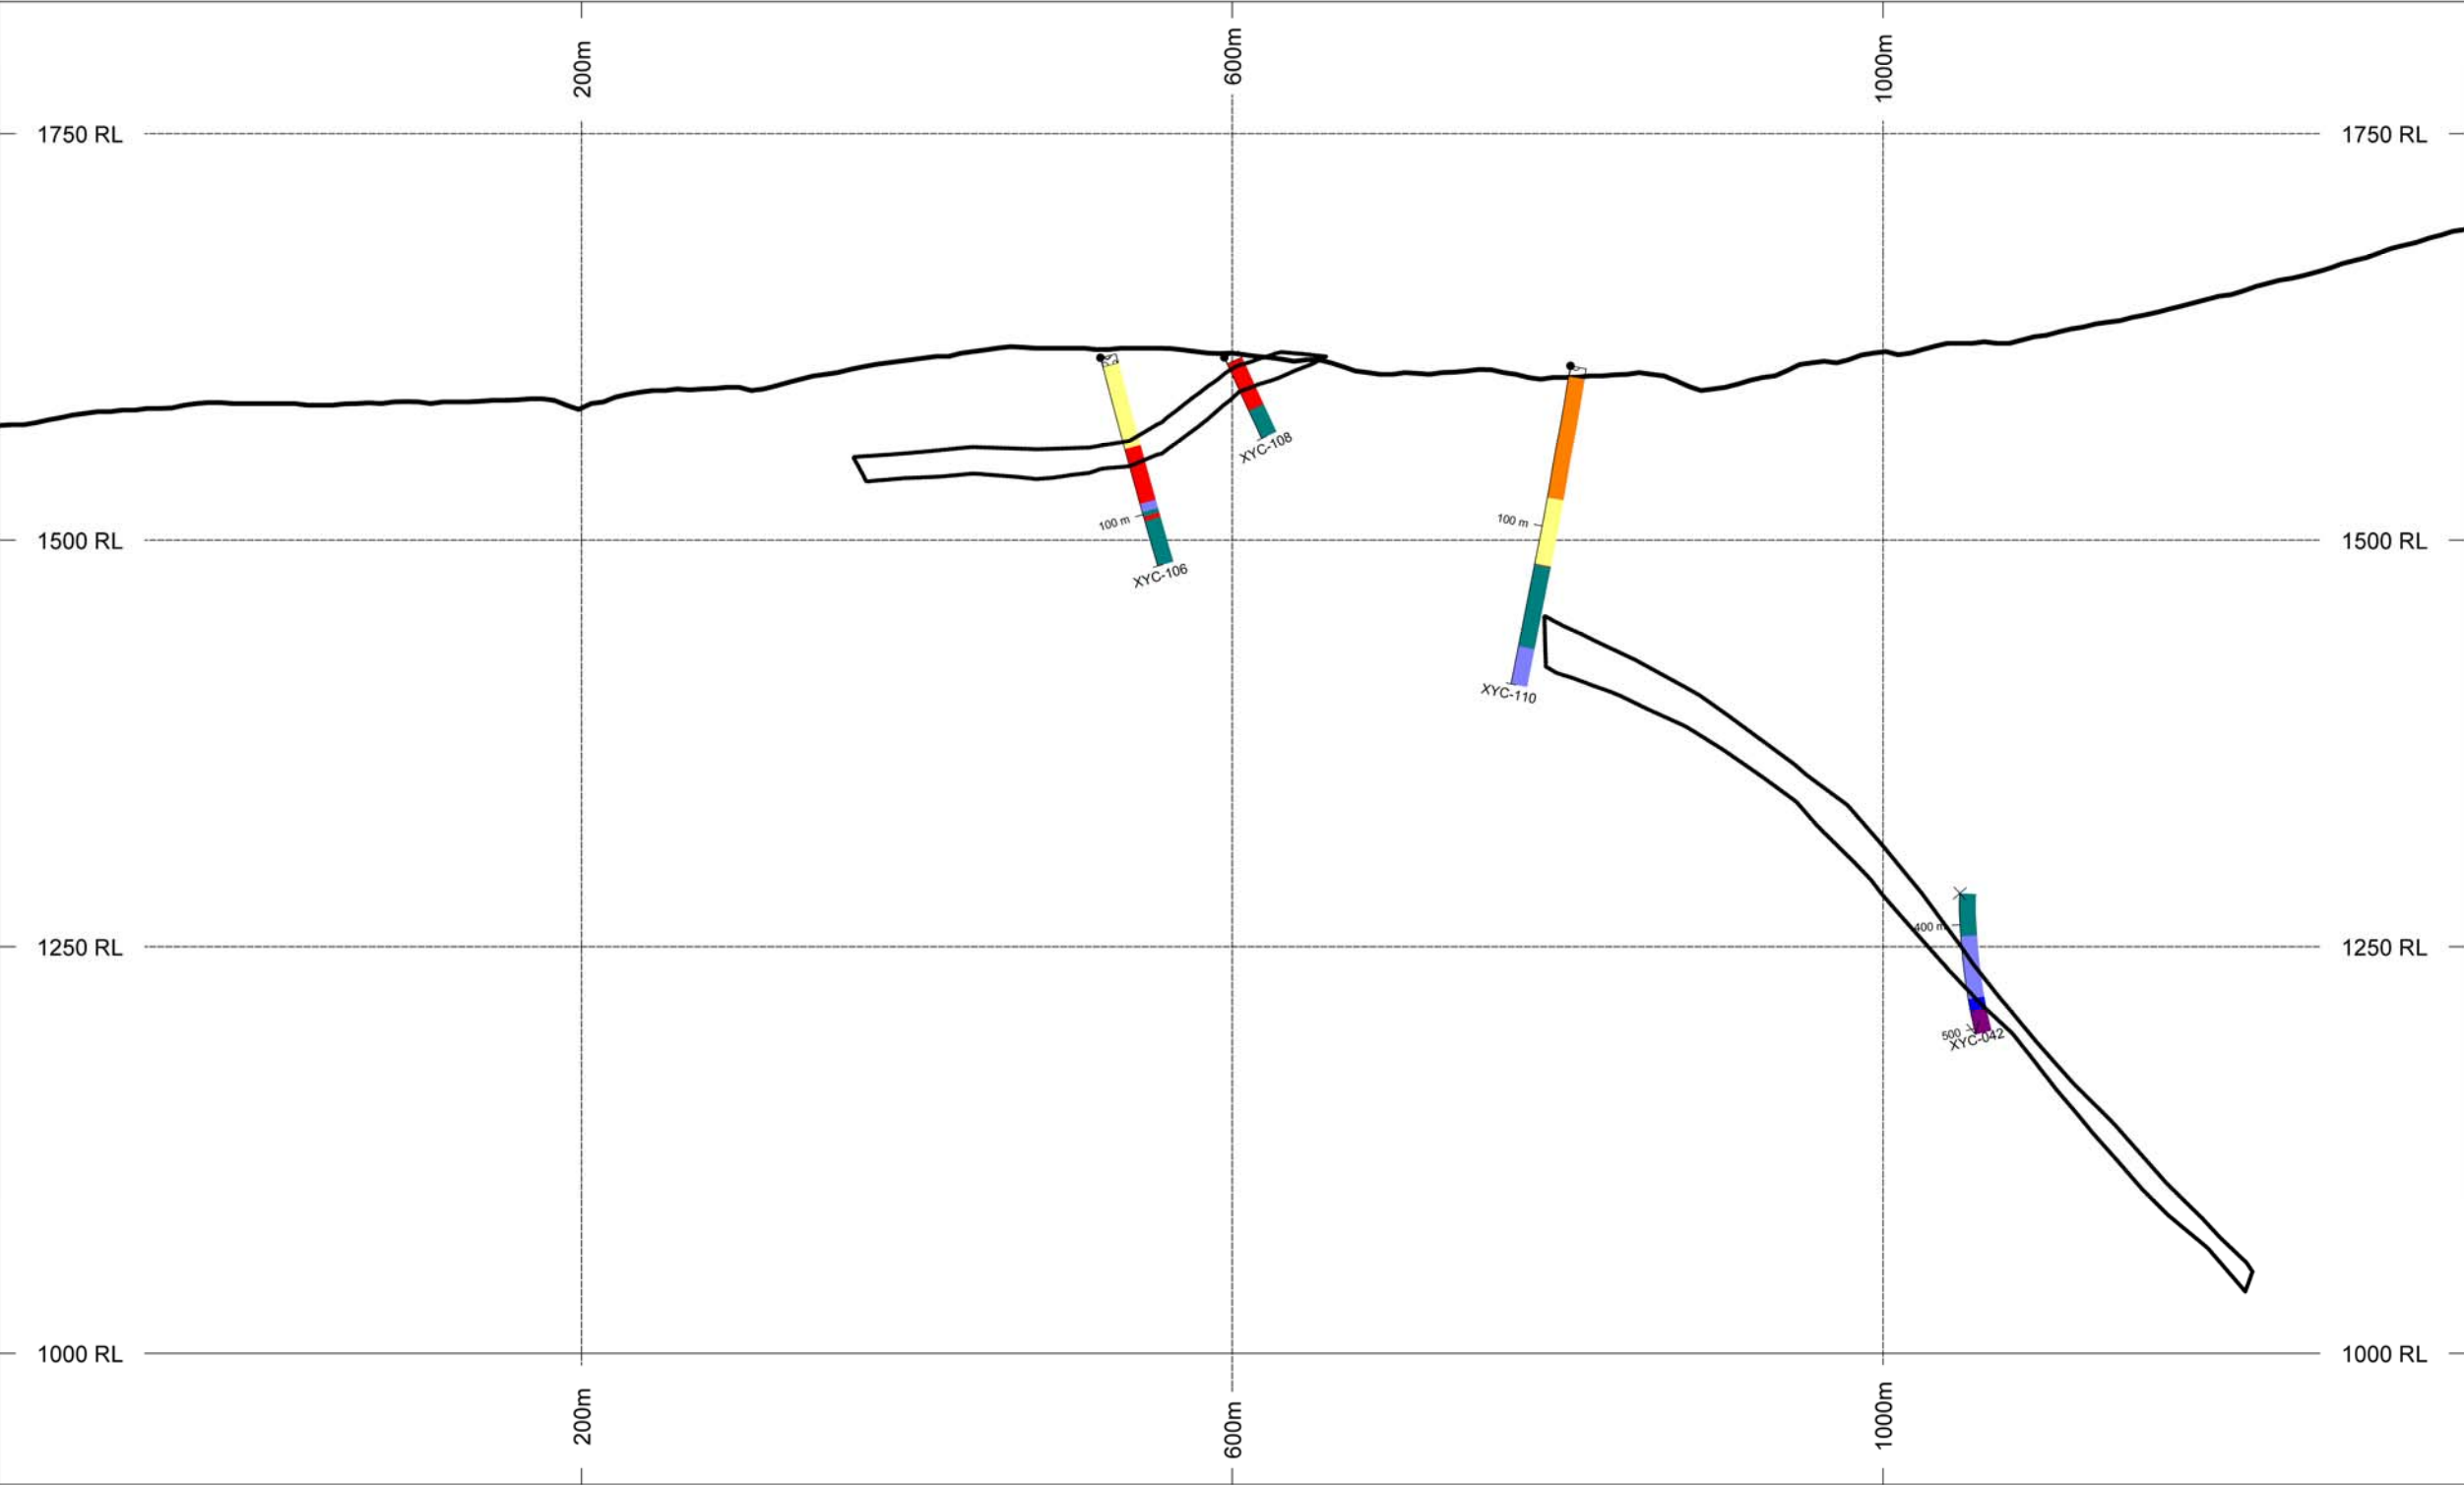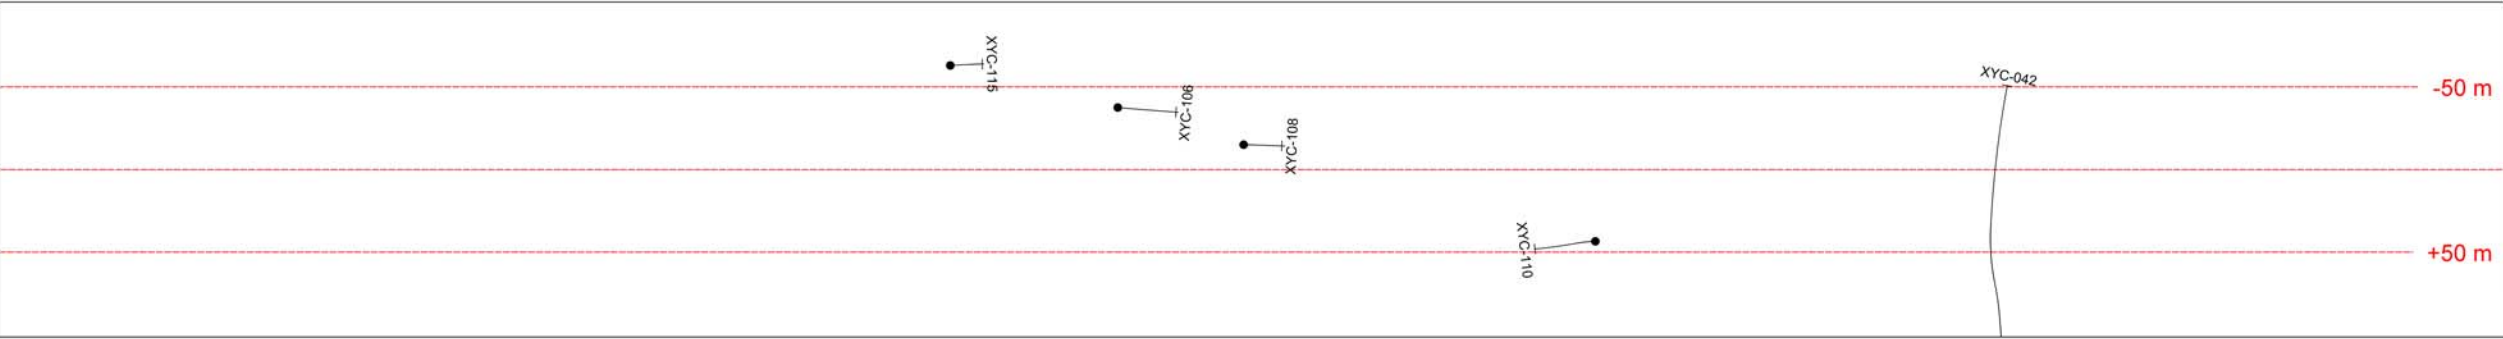

HOLES PLOTTED

TOTAL 4


XYZ-042 XYZ-106 XYZ-108 XYZ-110





ROCK CODES	PAT	LABEL	DESCRIPTION
rocktype		BSSM	Backside Siliceous Mudstone
		FLMD	Flaggy Mudstone
		USMS	Upper Siliceous Mudstone
		ACTM	Active Member
		LCMS	Lower Cherty Mudstone
		CCMS	Calcareous Mudstone
		PSMS	Pyritic Mudstone
		TRAN	Transition Formation
		CLST	Cambrian Limestone
		OVBR	Overburden
		FLT	Fault
		MDST	Undefined Mudstone

SECTION SPECS:

REF. PT. E, N	489645 m	6926128 m
EXTENTS	1516 m	911.9 m
SECTION TOP, BOT	1831 m	919.3 m
TOLERANCE +/-	50 m	

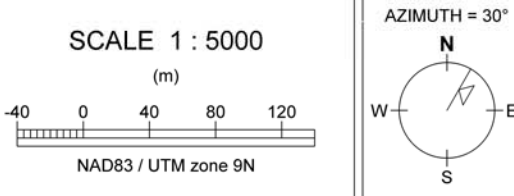

Selwyn Chihong Mining Ltd.
Selwyn Project, YT
Section L_01600N/0600E
XY Central Deposit

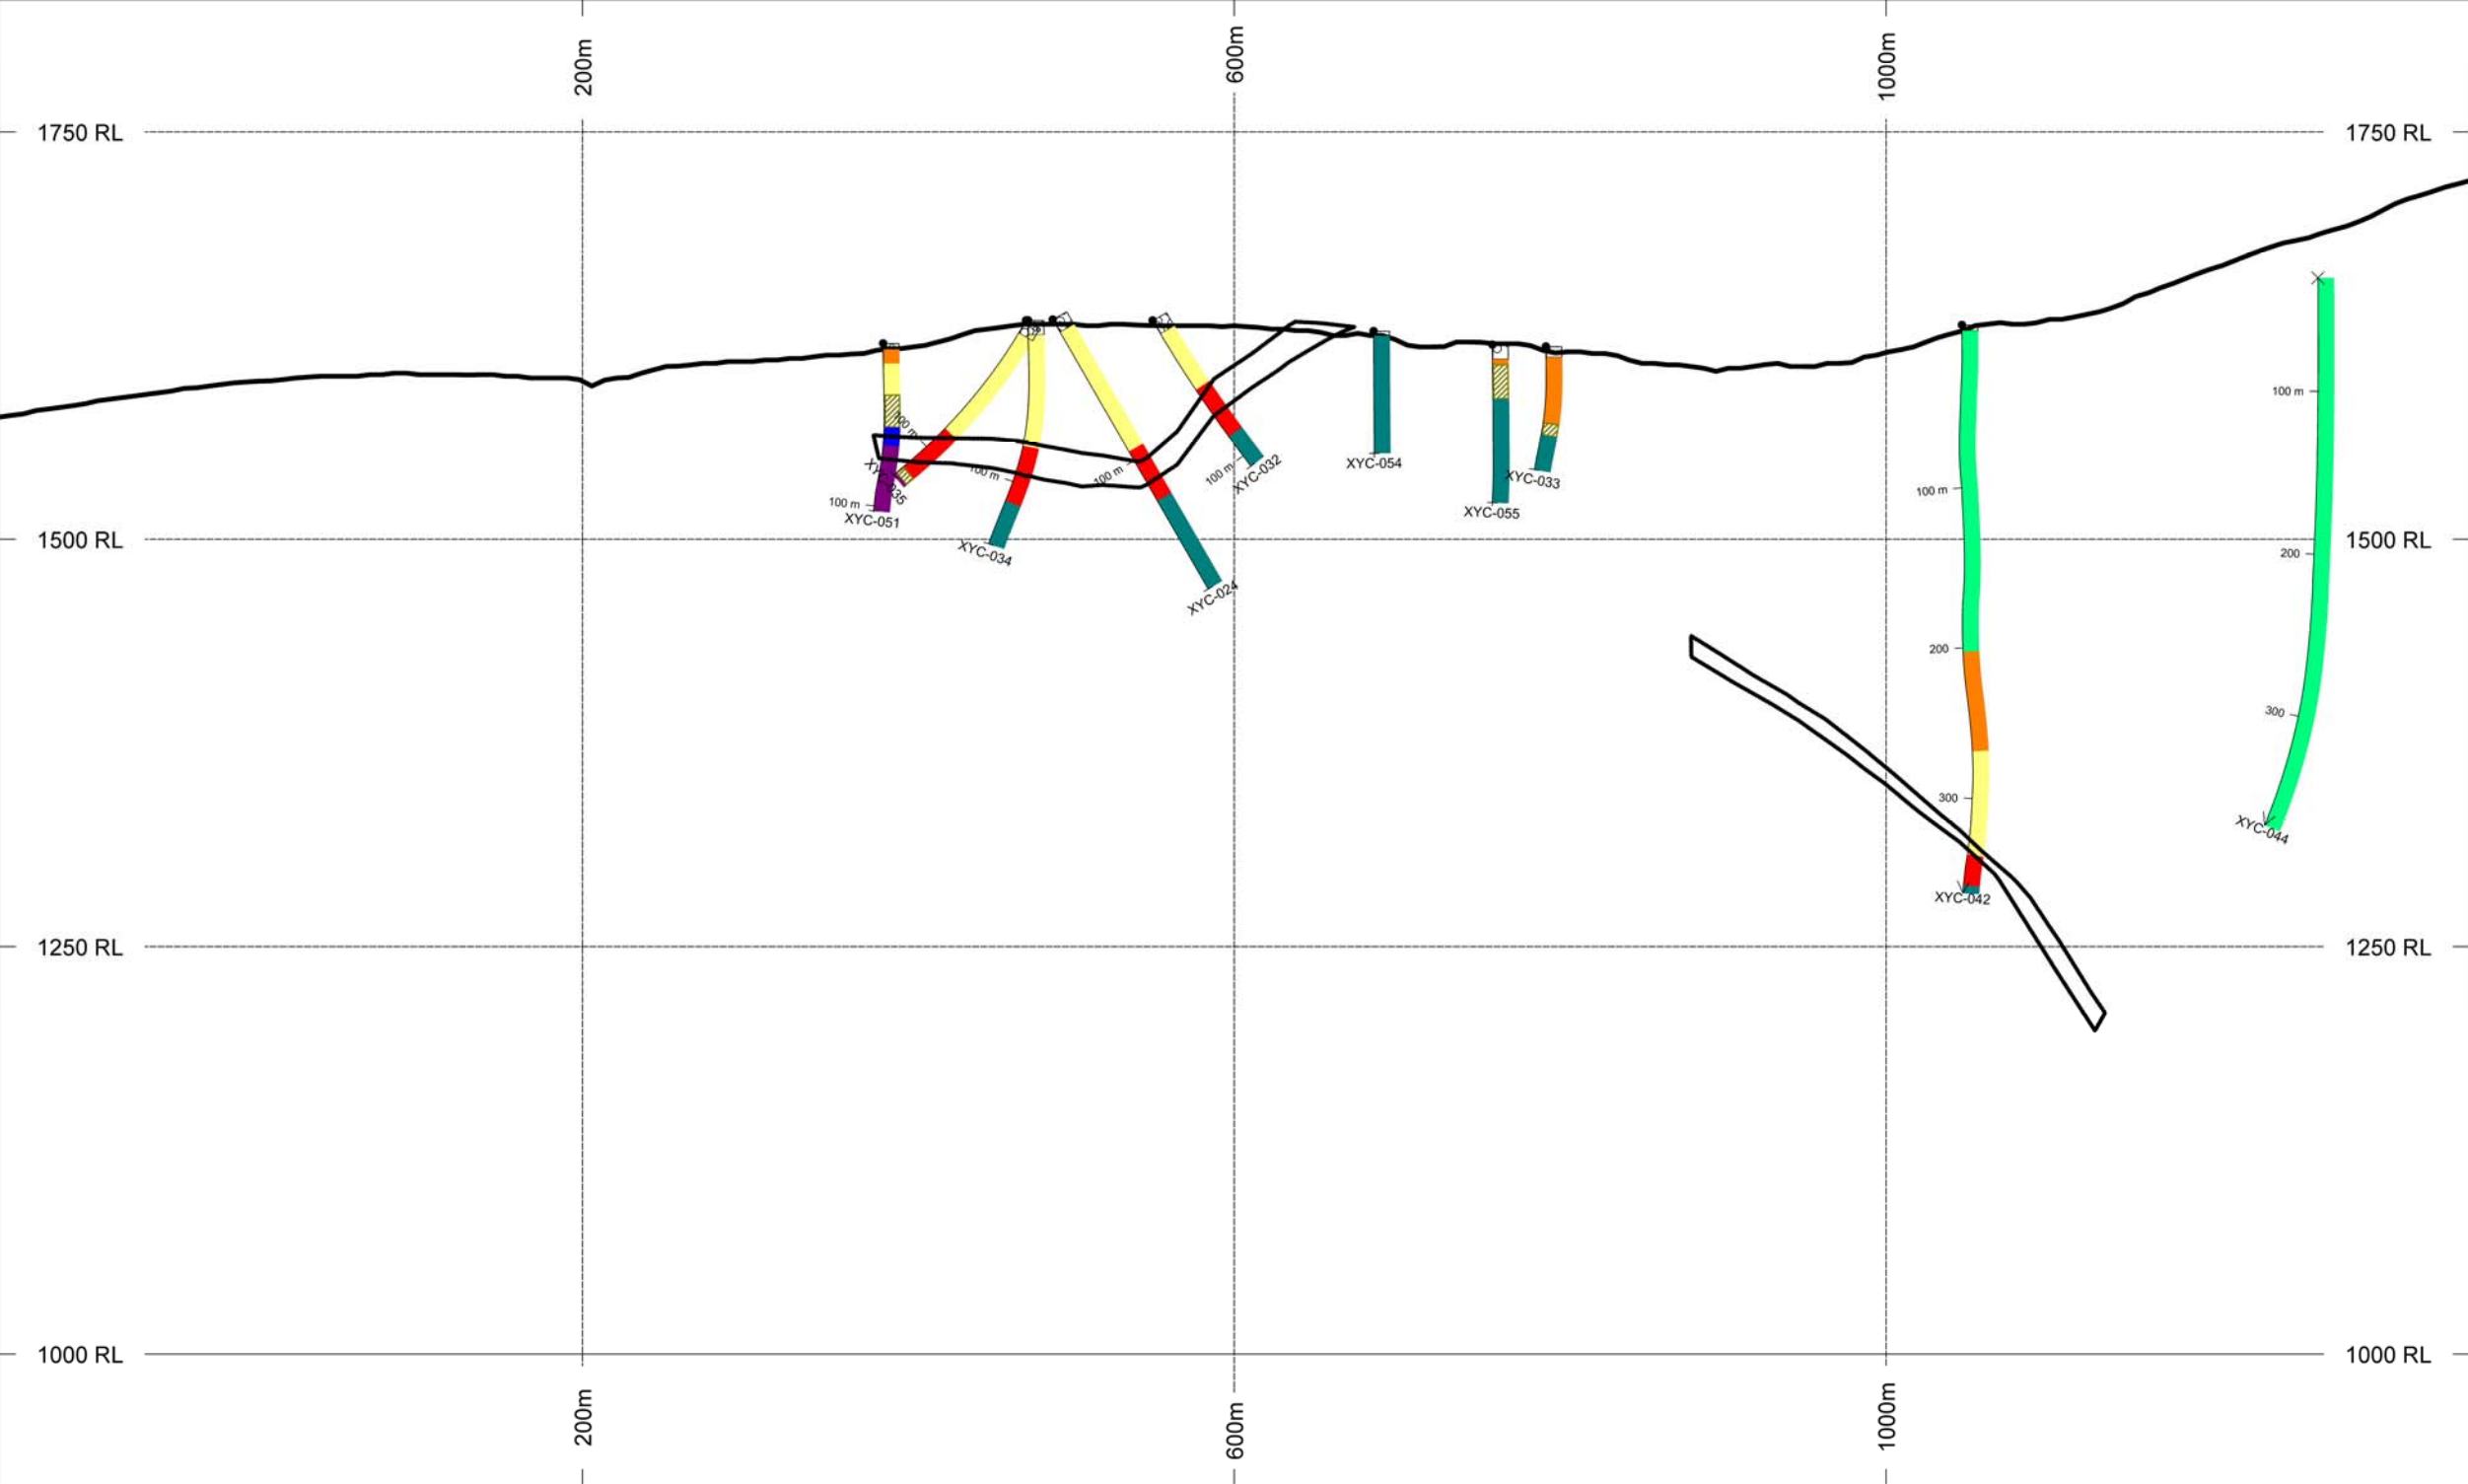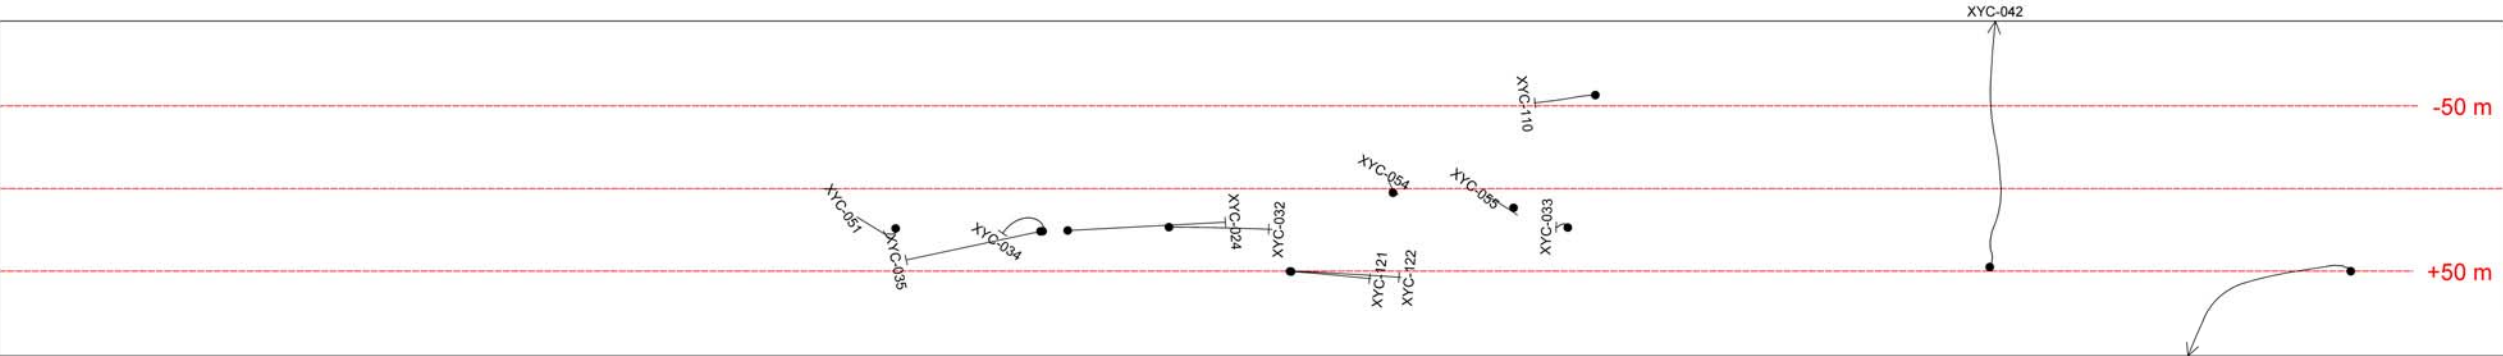

HOLES PLOTTED

TOTAL 10


XYC-024	XYC-032	XYC-033	XYC-034
XYC-035	XYC-042	XYC-044	XYC-051
XYC-054	XYC-055		





ROCK CODES rocktype	PAT	LABEL	DESCRIPTION
		BSSM	Backside Siliceous Mudstone
		FLMD	Flaggy Mudstone
		USMS	Upper Siliceous Mudstone
		ACTM	Active Member
		LCMS	Lower Cherty Mudstone
		CCMS	Calcareous Mudstone
		PSMS	Pyritic Mudstone
		TRAN	Transition Formation
		CLST	Cambrian Limestone
		OVBR	Overburden
		FLT	Fault
		MDST	Undefined Mudstone

SECTION SPECS:

REF. PT. E, N	489732 m	6926078 m
EXTENTS	1516 m	911.9 m
SECTION TOP, BOT	1831 m	919.3 m
TOLERANCE +/-	50 m	

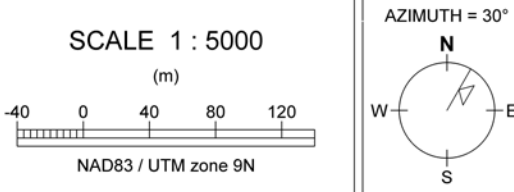

Selwyn Chihong Mining Ltd.
Selwyn Project, YT
Section L_01500N/0600E
XY Central Deposit

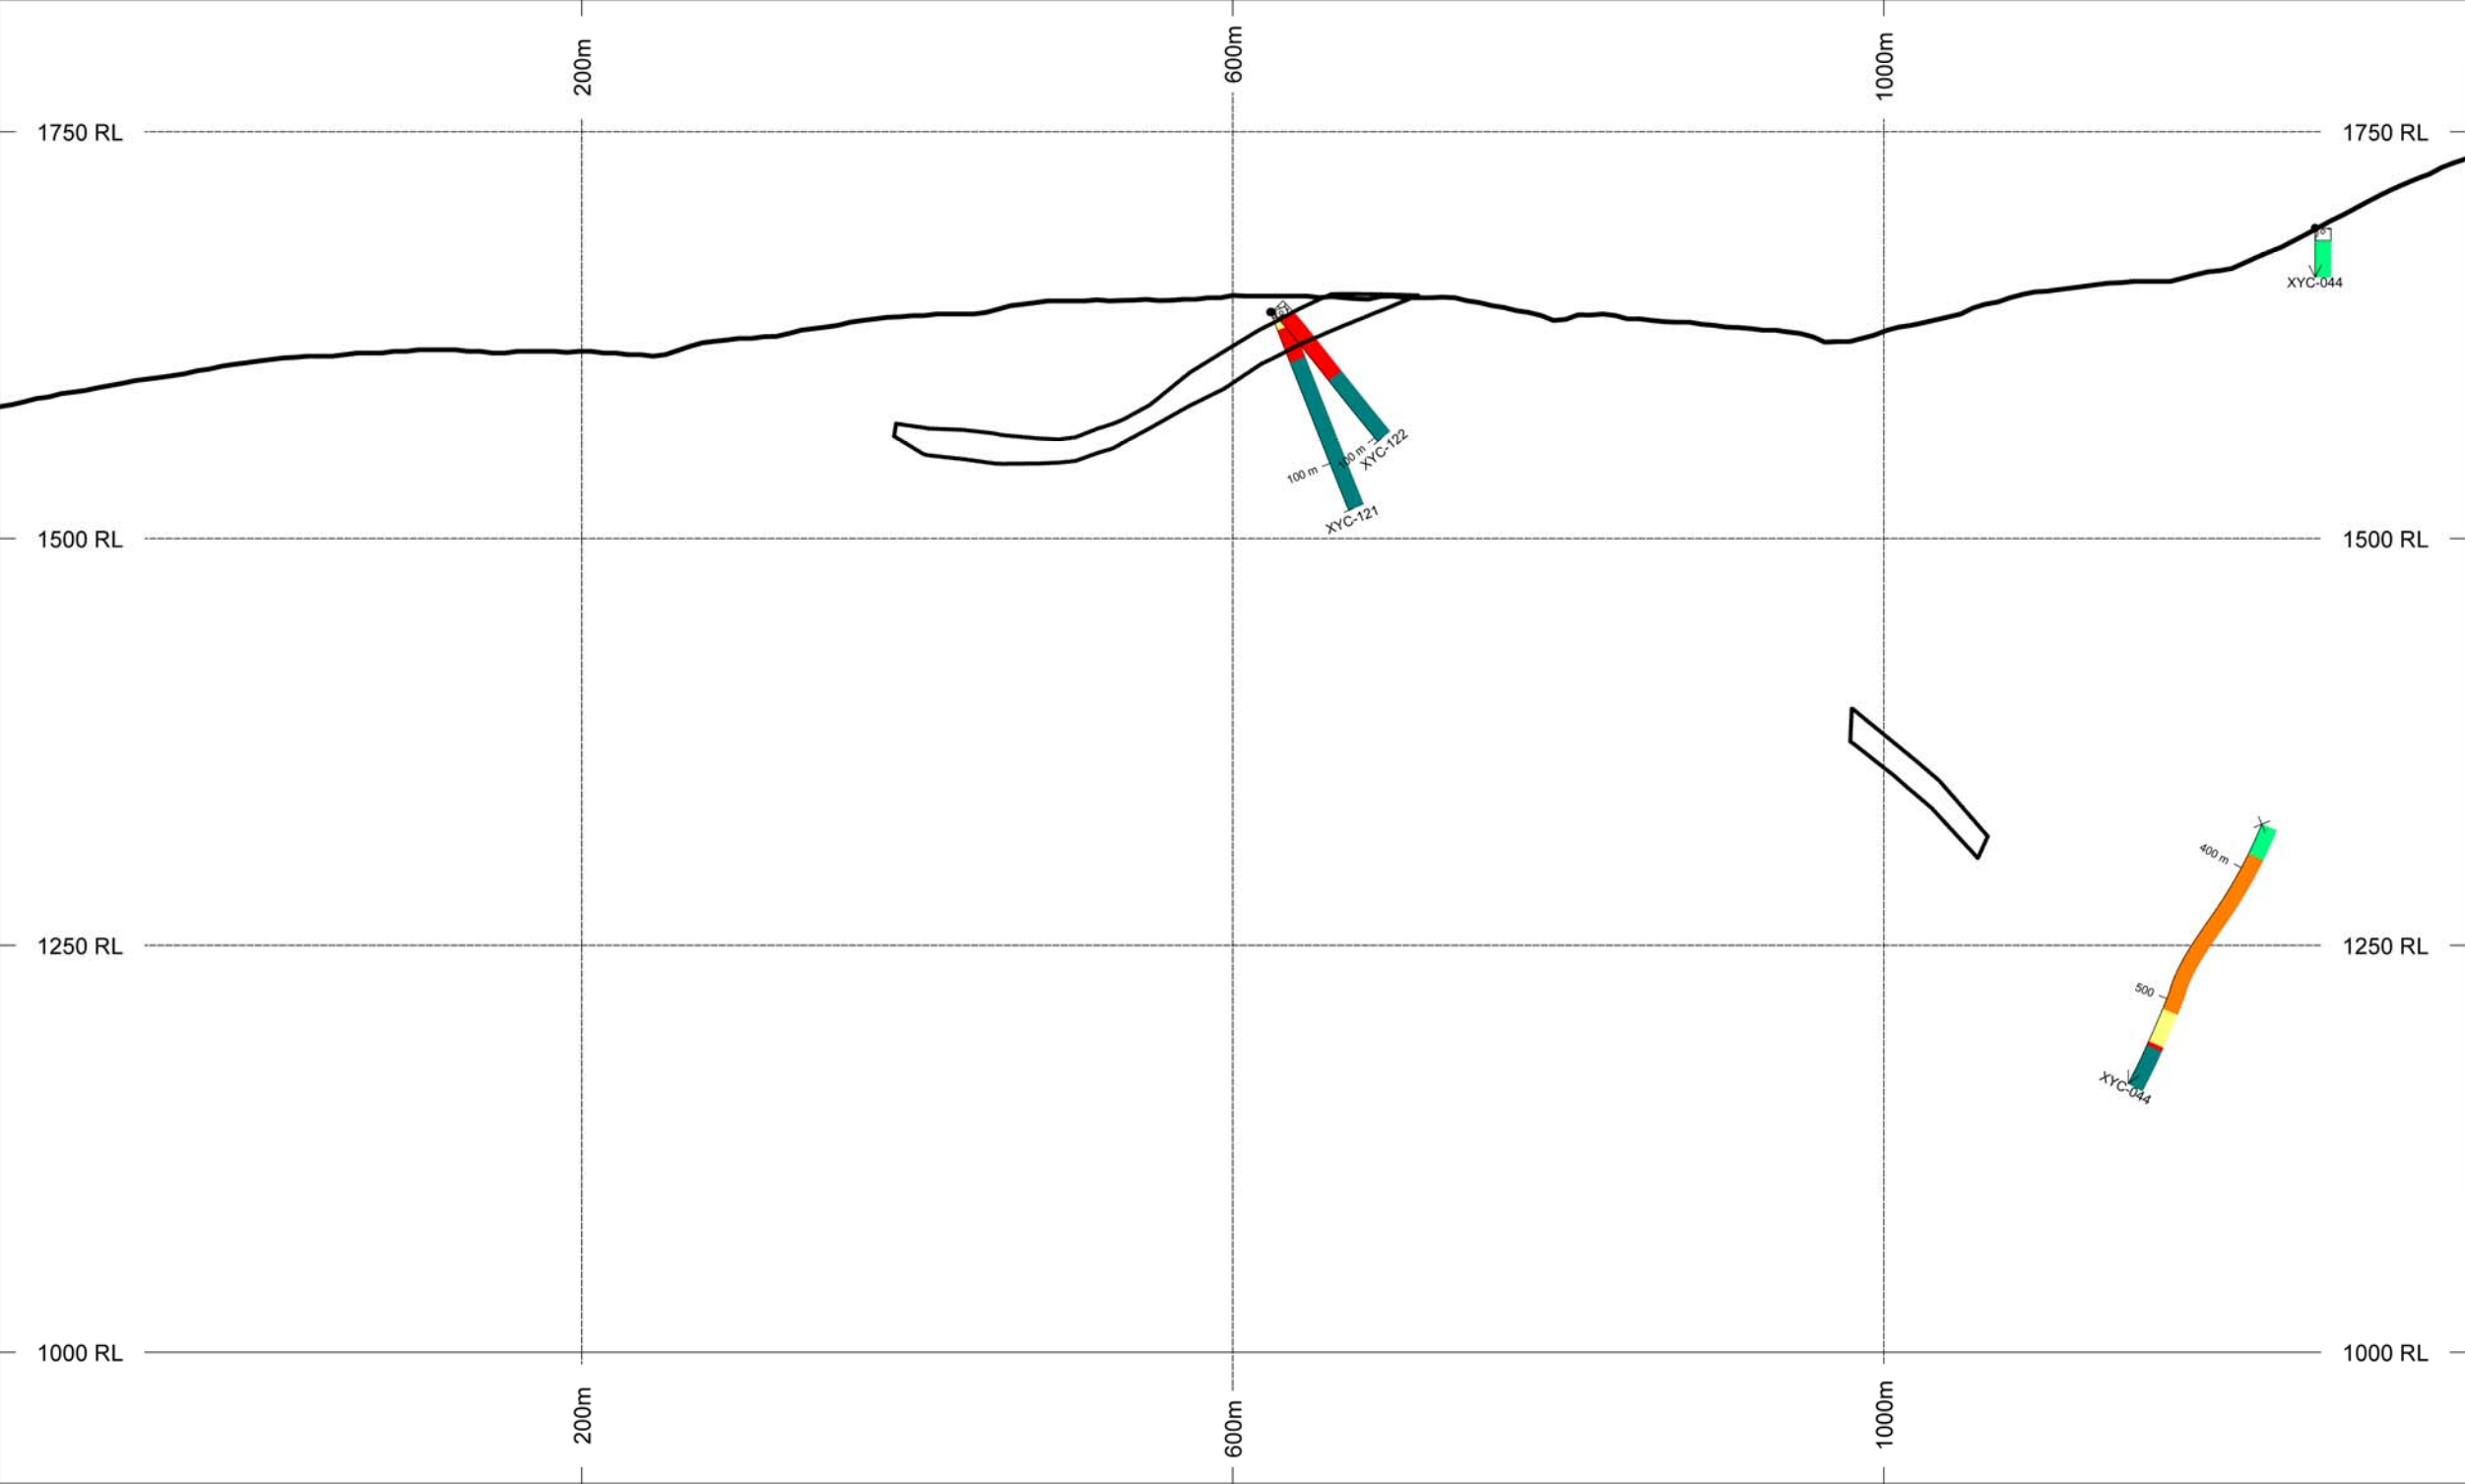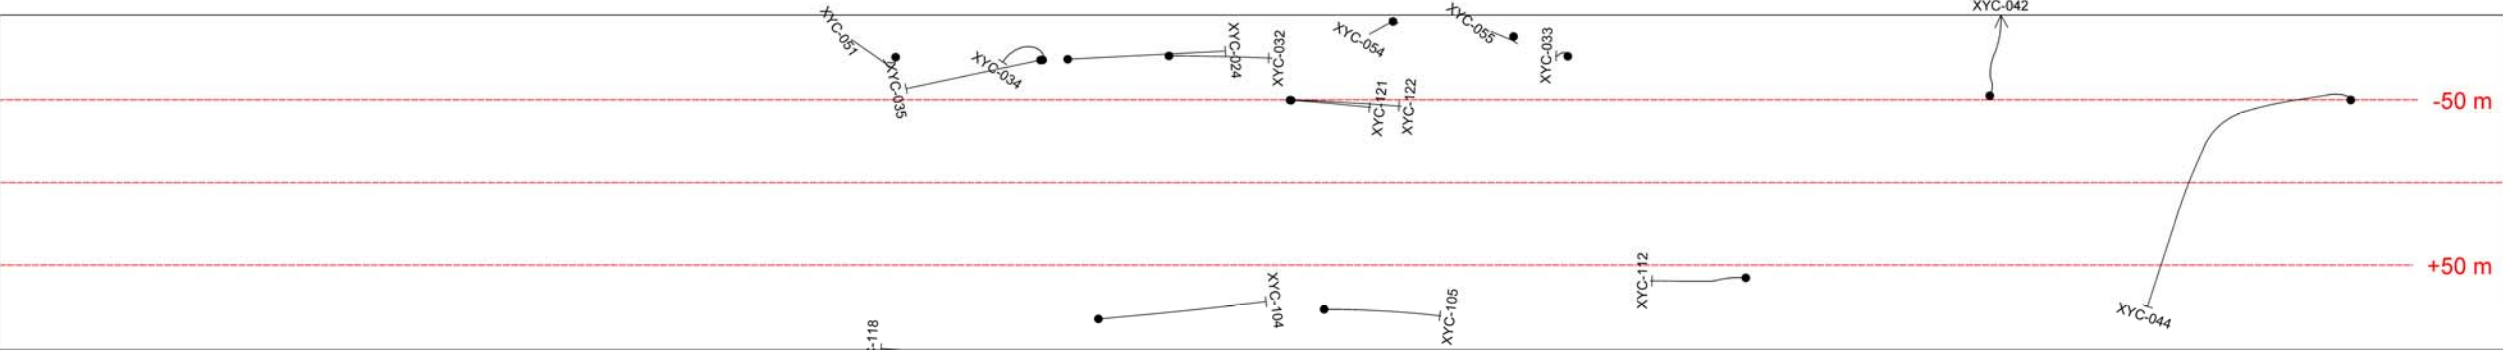

HOLES PLOTTED

TOTAL 3


XYC-044 XYC-121 XYC-122





ROCK CODES	PAT	LABEL	DESCRIPTION
rocktype		BSSM	Backside Siliceous Mudstone
		FLMD	Flaggy Mudstone
		USMS	Upper Siliceous Mudstone
		ACTM	Active Member
		LCMS	Lower Cherty Mudstone
		CCMS	Calcareous Mudstone
		PSMS	Pyritic Mudstone
		TRAN	Transition Formation
		CLST	Cambrian Limestone
		OVBR	Overburden
		FLT	Fault
		MDST	Undefined Mudstone

SECTION SPECS:

REF. PT. E, N	489818 m	6926028 m
EXTENTS	1516 m	911.9 m
SECTION TOP, BOT	1831 m	919.3 m
TOLERANCE +/-	50 m	

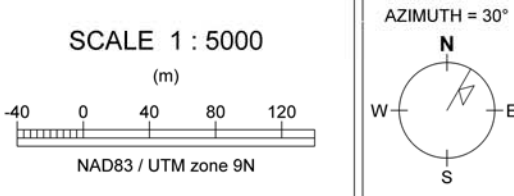

Selwyn Chihong Mining Ltd.
Selwyn Project, YT
Section L_01400N/0600E
XY Central Deposit

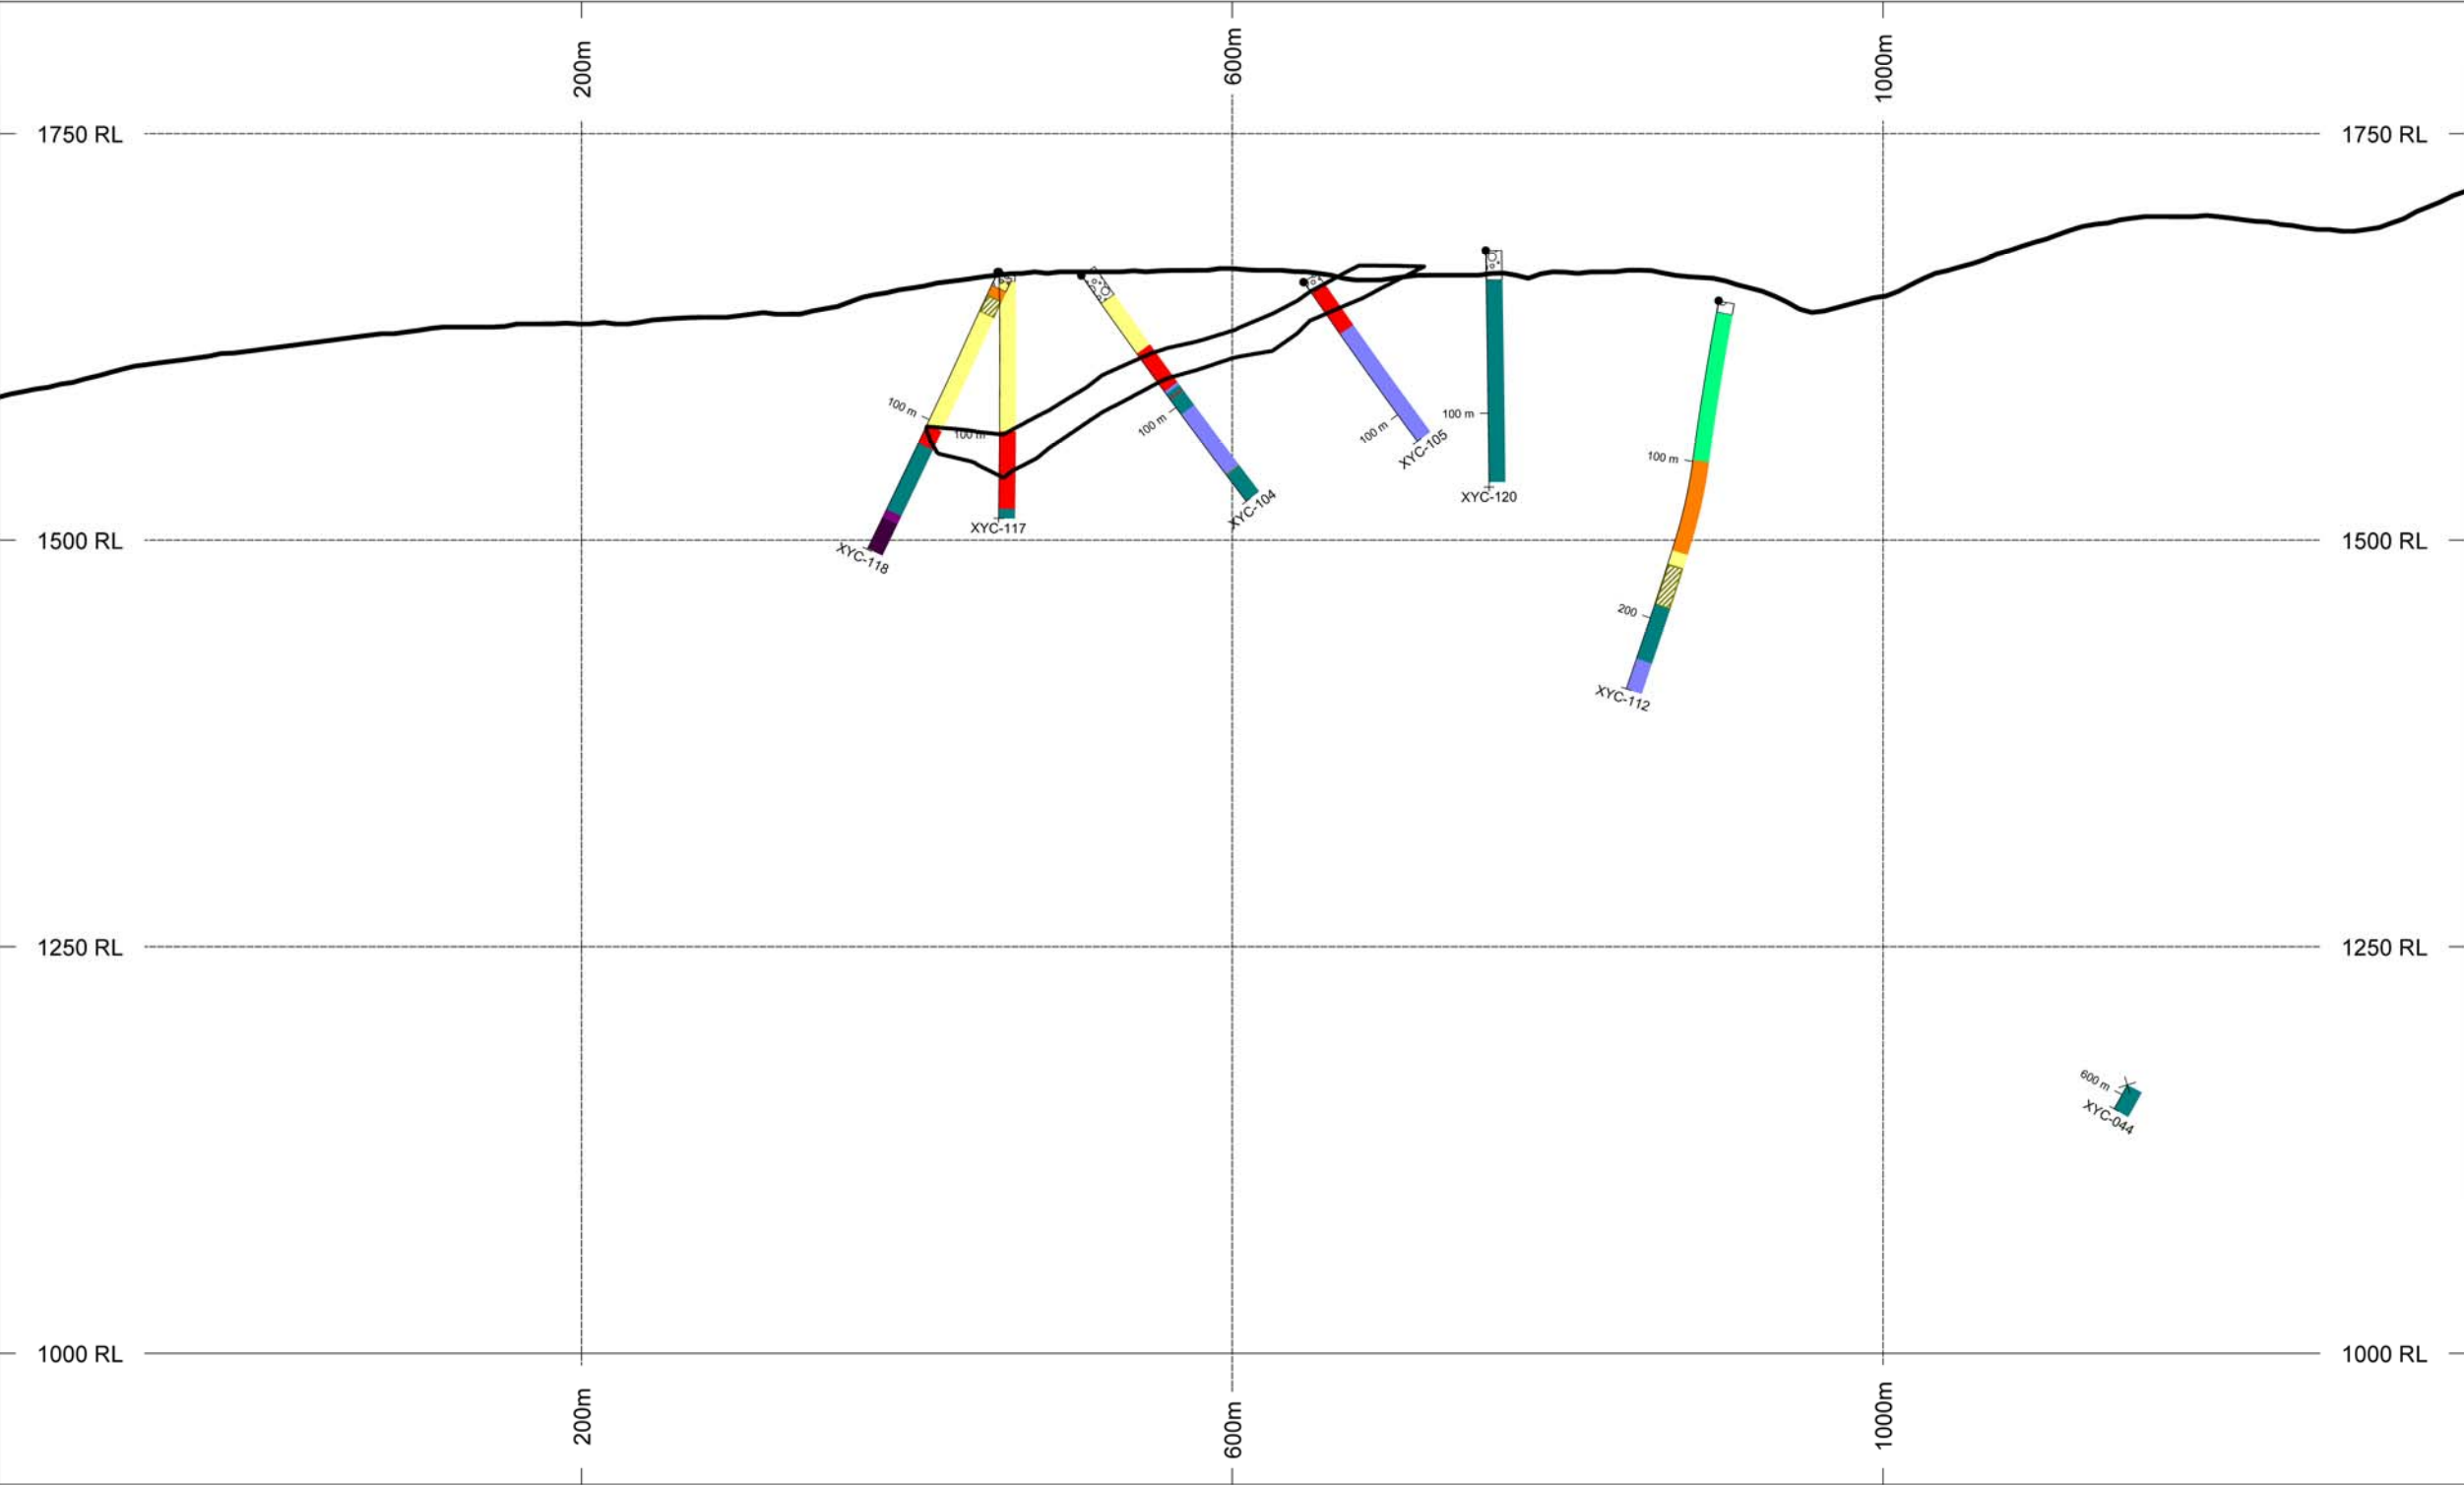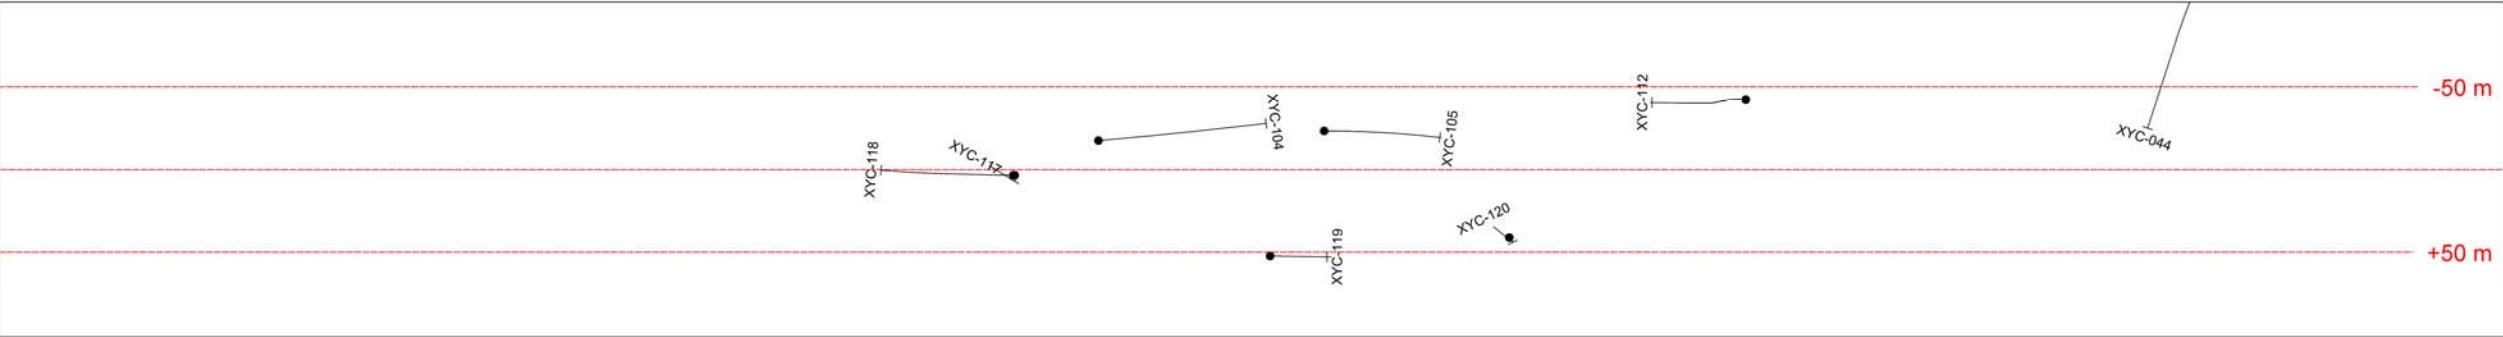

HOLES PLOTTED

TOTAL 7

XYC-044	XYC-104	XYC-105	XYC-112
XYC-117	XYC-118	XYC-120	




SELWYN CHIHONG
MINING LTD.



ROCK CODES	PAT	LABEL	DESCRIPTION
rocktype		BSSM	Backside Siliceous Mudstone
		FLMD	Flaggy Mudstone
		USMS	Upper Siliceous Mudstone
		ACTM	Active Member
		LCMS	Lower Cherty Mudstone
		CCMS	Calcareous Mudstone
		PSMS	Pyritic Mudstone
		TRAN	Transition Formation
		CLST	Cambrian Limestone
		OVBR	Overburden
		FLT	Fault
		MDST	Undefined Mudstone

SECTION SPECS:

REF. PT. E, N	489905 m	6925978 m
EXTENTS	1516 m	911.9 m
SECTION TOP, BOT	1831 m	919.3 m
TOLERANCE +/-	50 m	

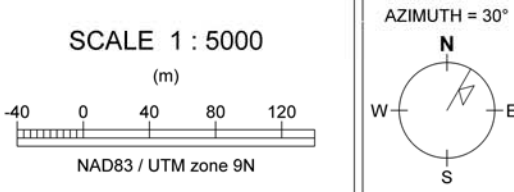

Selwyn Chihong Mining Ltd.
Selwyn Project, YT
Section L_01300N/0600E
XY Central Deposit

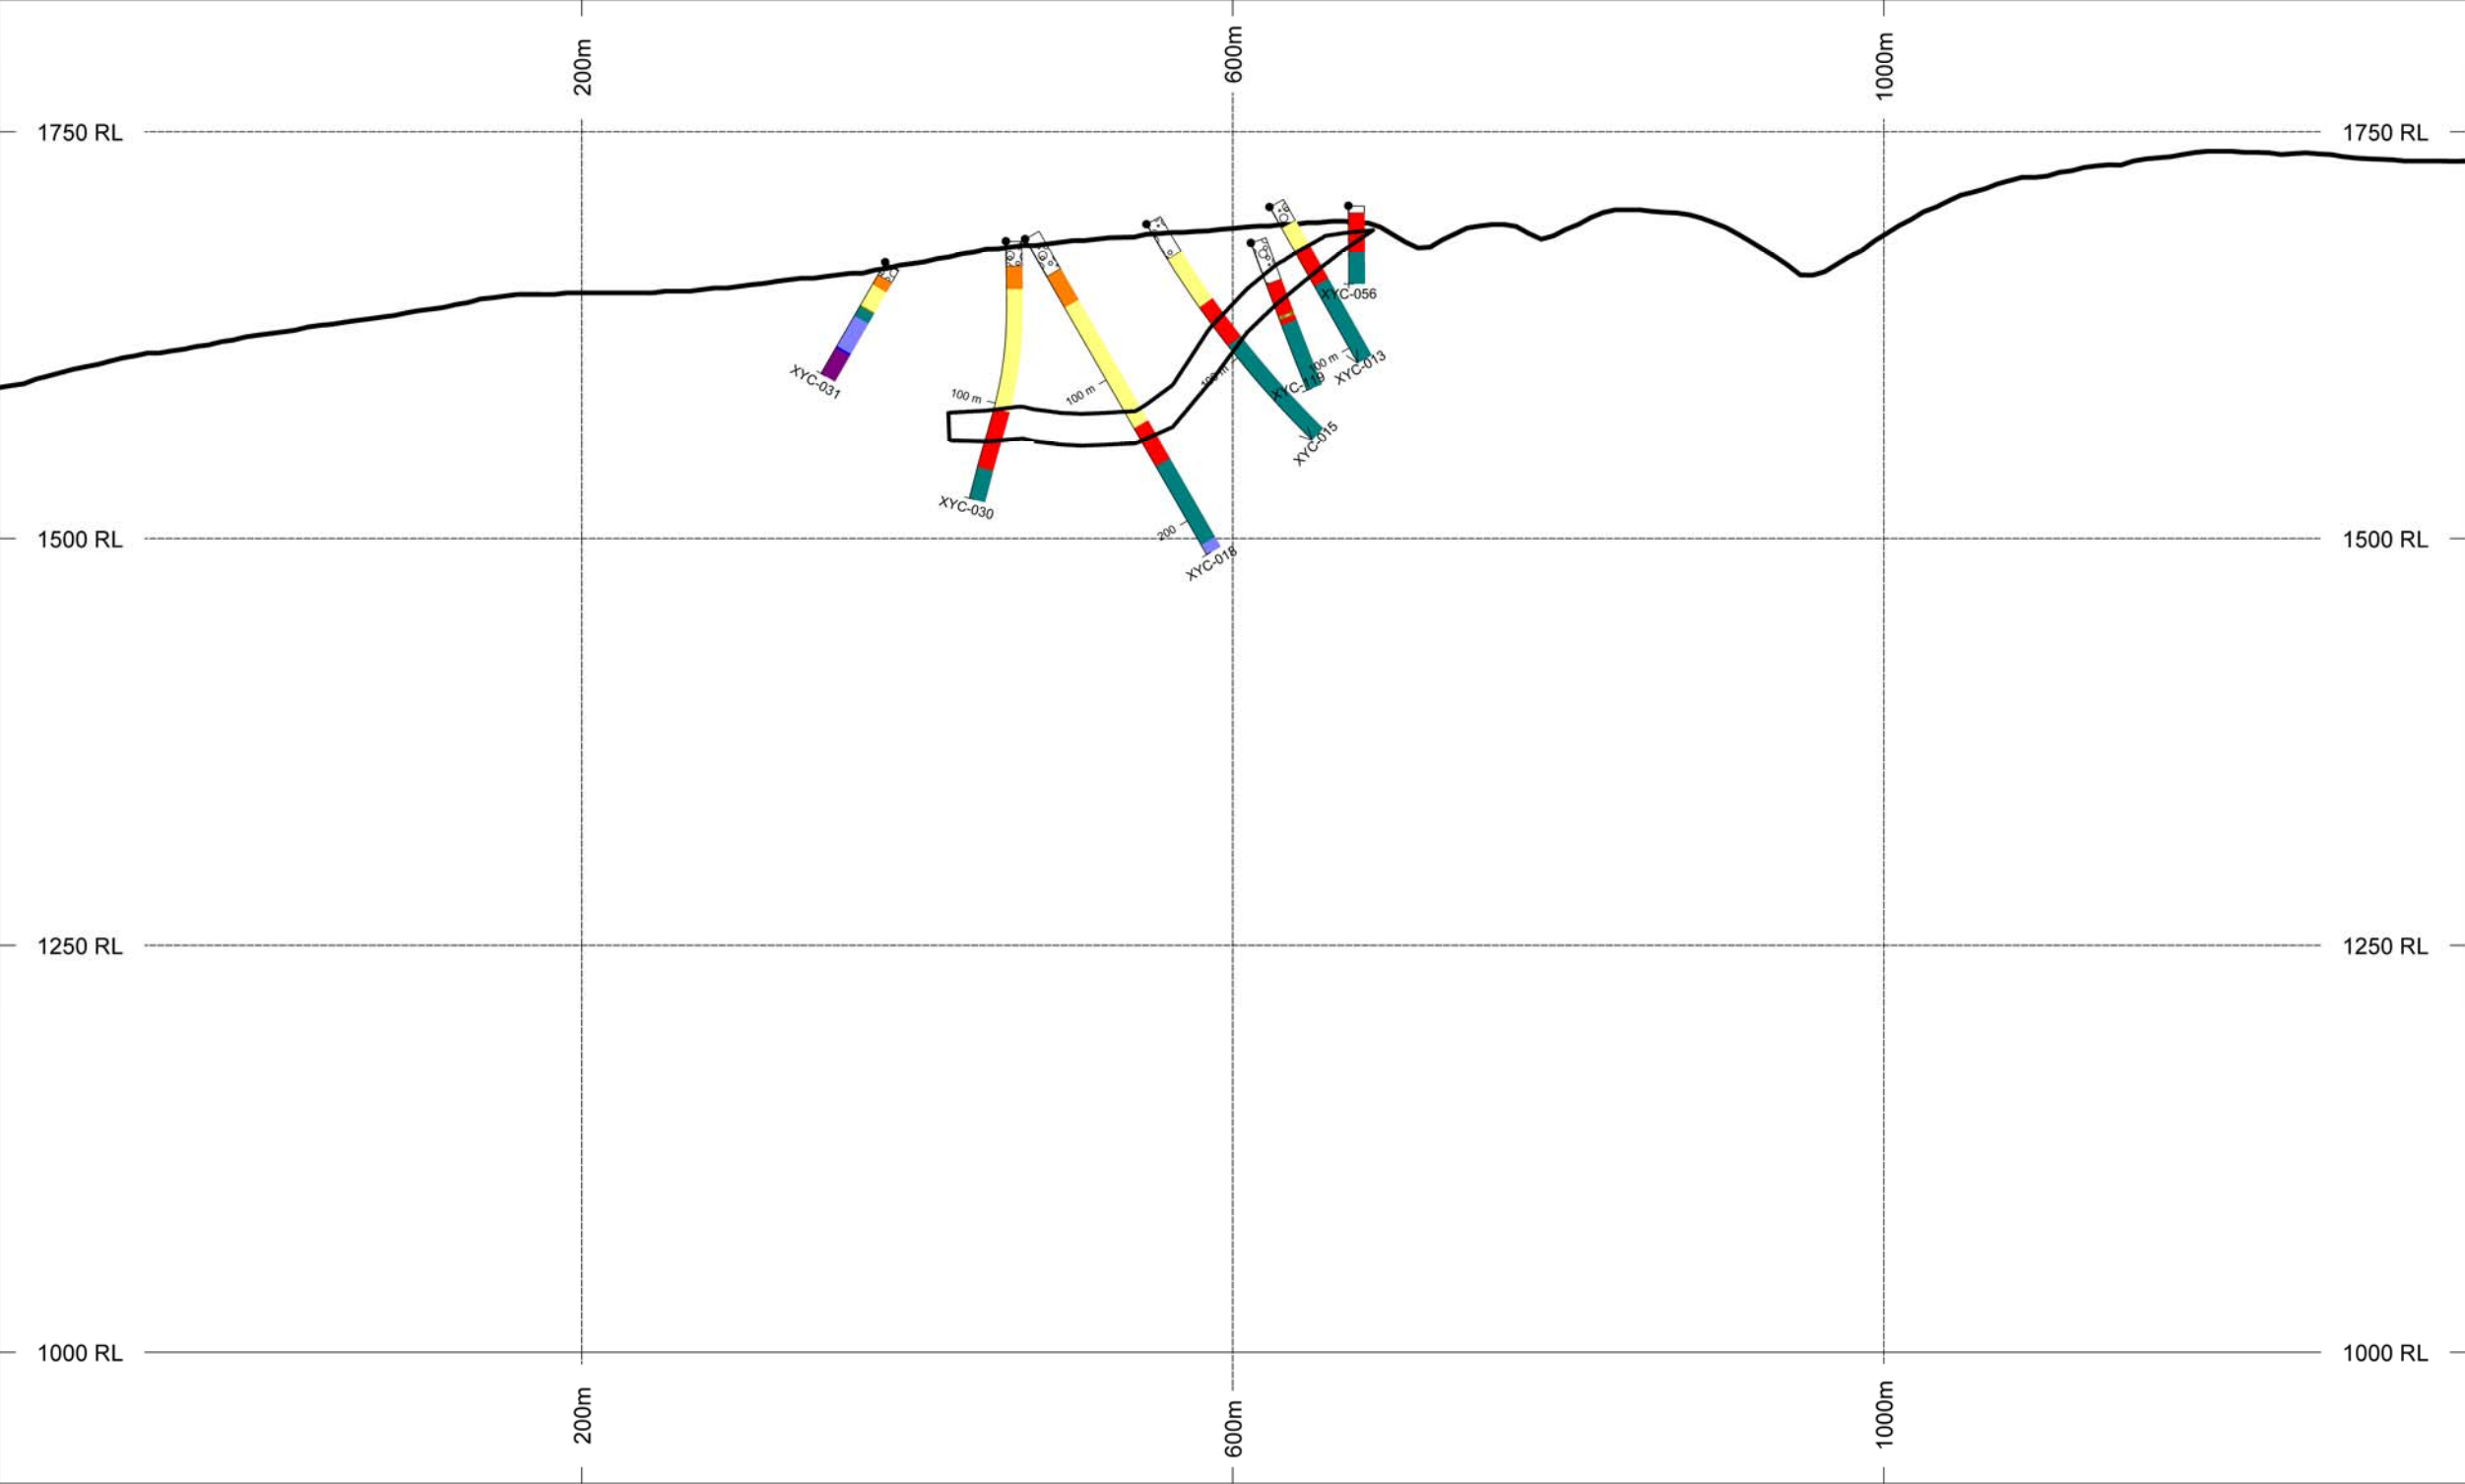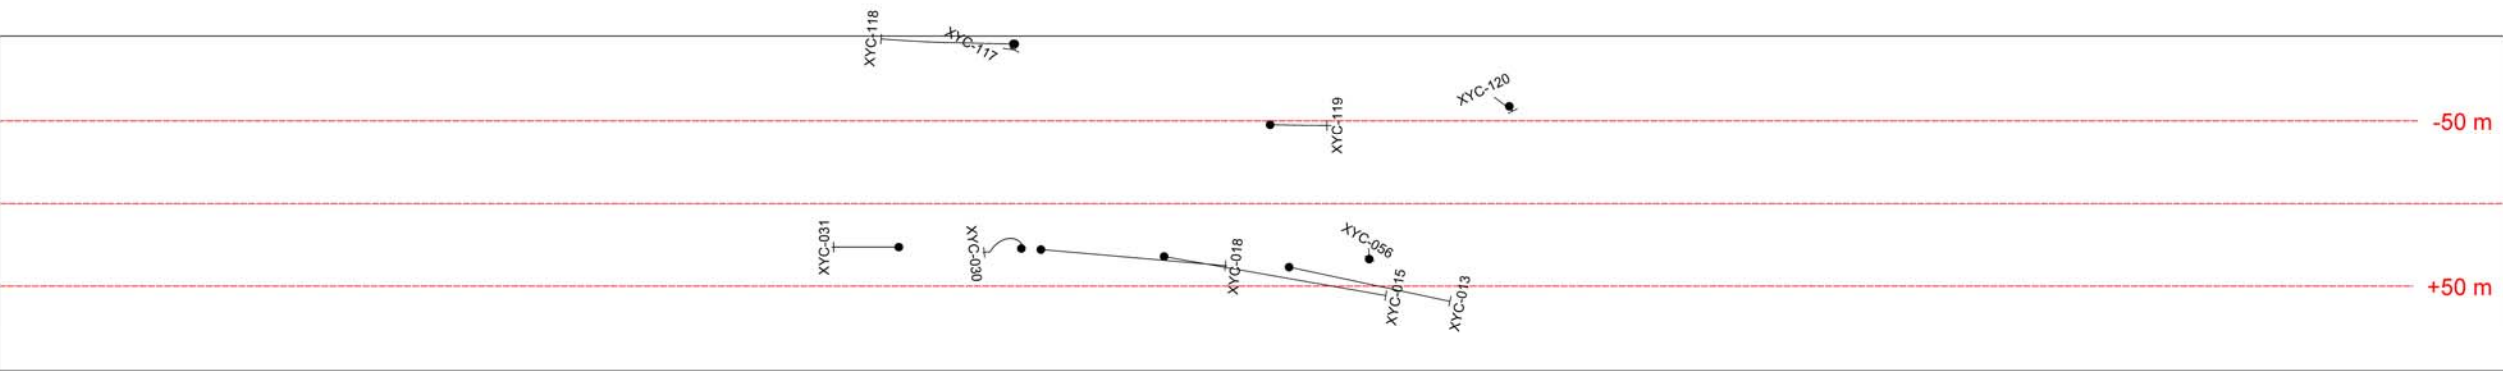

HOLES PLOTTED

TOTAL 7


XYC-013	XYC-015	XYC-018	XYC-030
XYC-031	XYC-056	XYC-119	





ROCK CODES	PAT	LABEL	DESCRIPTION
rocktype			
		FLMD	Flaggy Mudstone
		USMS	Upper Siliceous Mudstone
		ACTM	Active Member
		LCMS	Lower Cherty Mudstone
		CCMS	Calcareous Mudstone
		PSMS	Pyritic Mudstone
		TRAN	Transition Formation
		CLST	Cambrian Limestone
		OVBR	Overburden
		FLT	Fault
		MDST	Undefined Mudstone

SECTION SPECS:

REF. PT. E, N	489992 m	6925928 m
EXTENTS	1516 m	911.9 m
SECTION TOP, BOT	1831 m	919.3 m
TOLERANCE +/-	50 m	

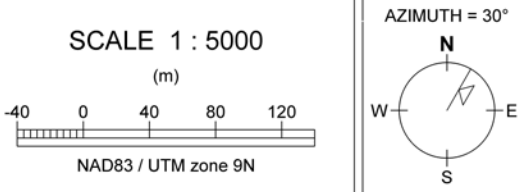

Selwyn Chihong Mining Ltd.
Selwyn Project, YT
Section L_01200N/0600E
XY Central Deposit

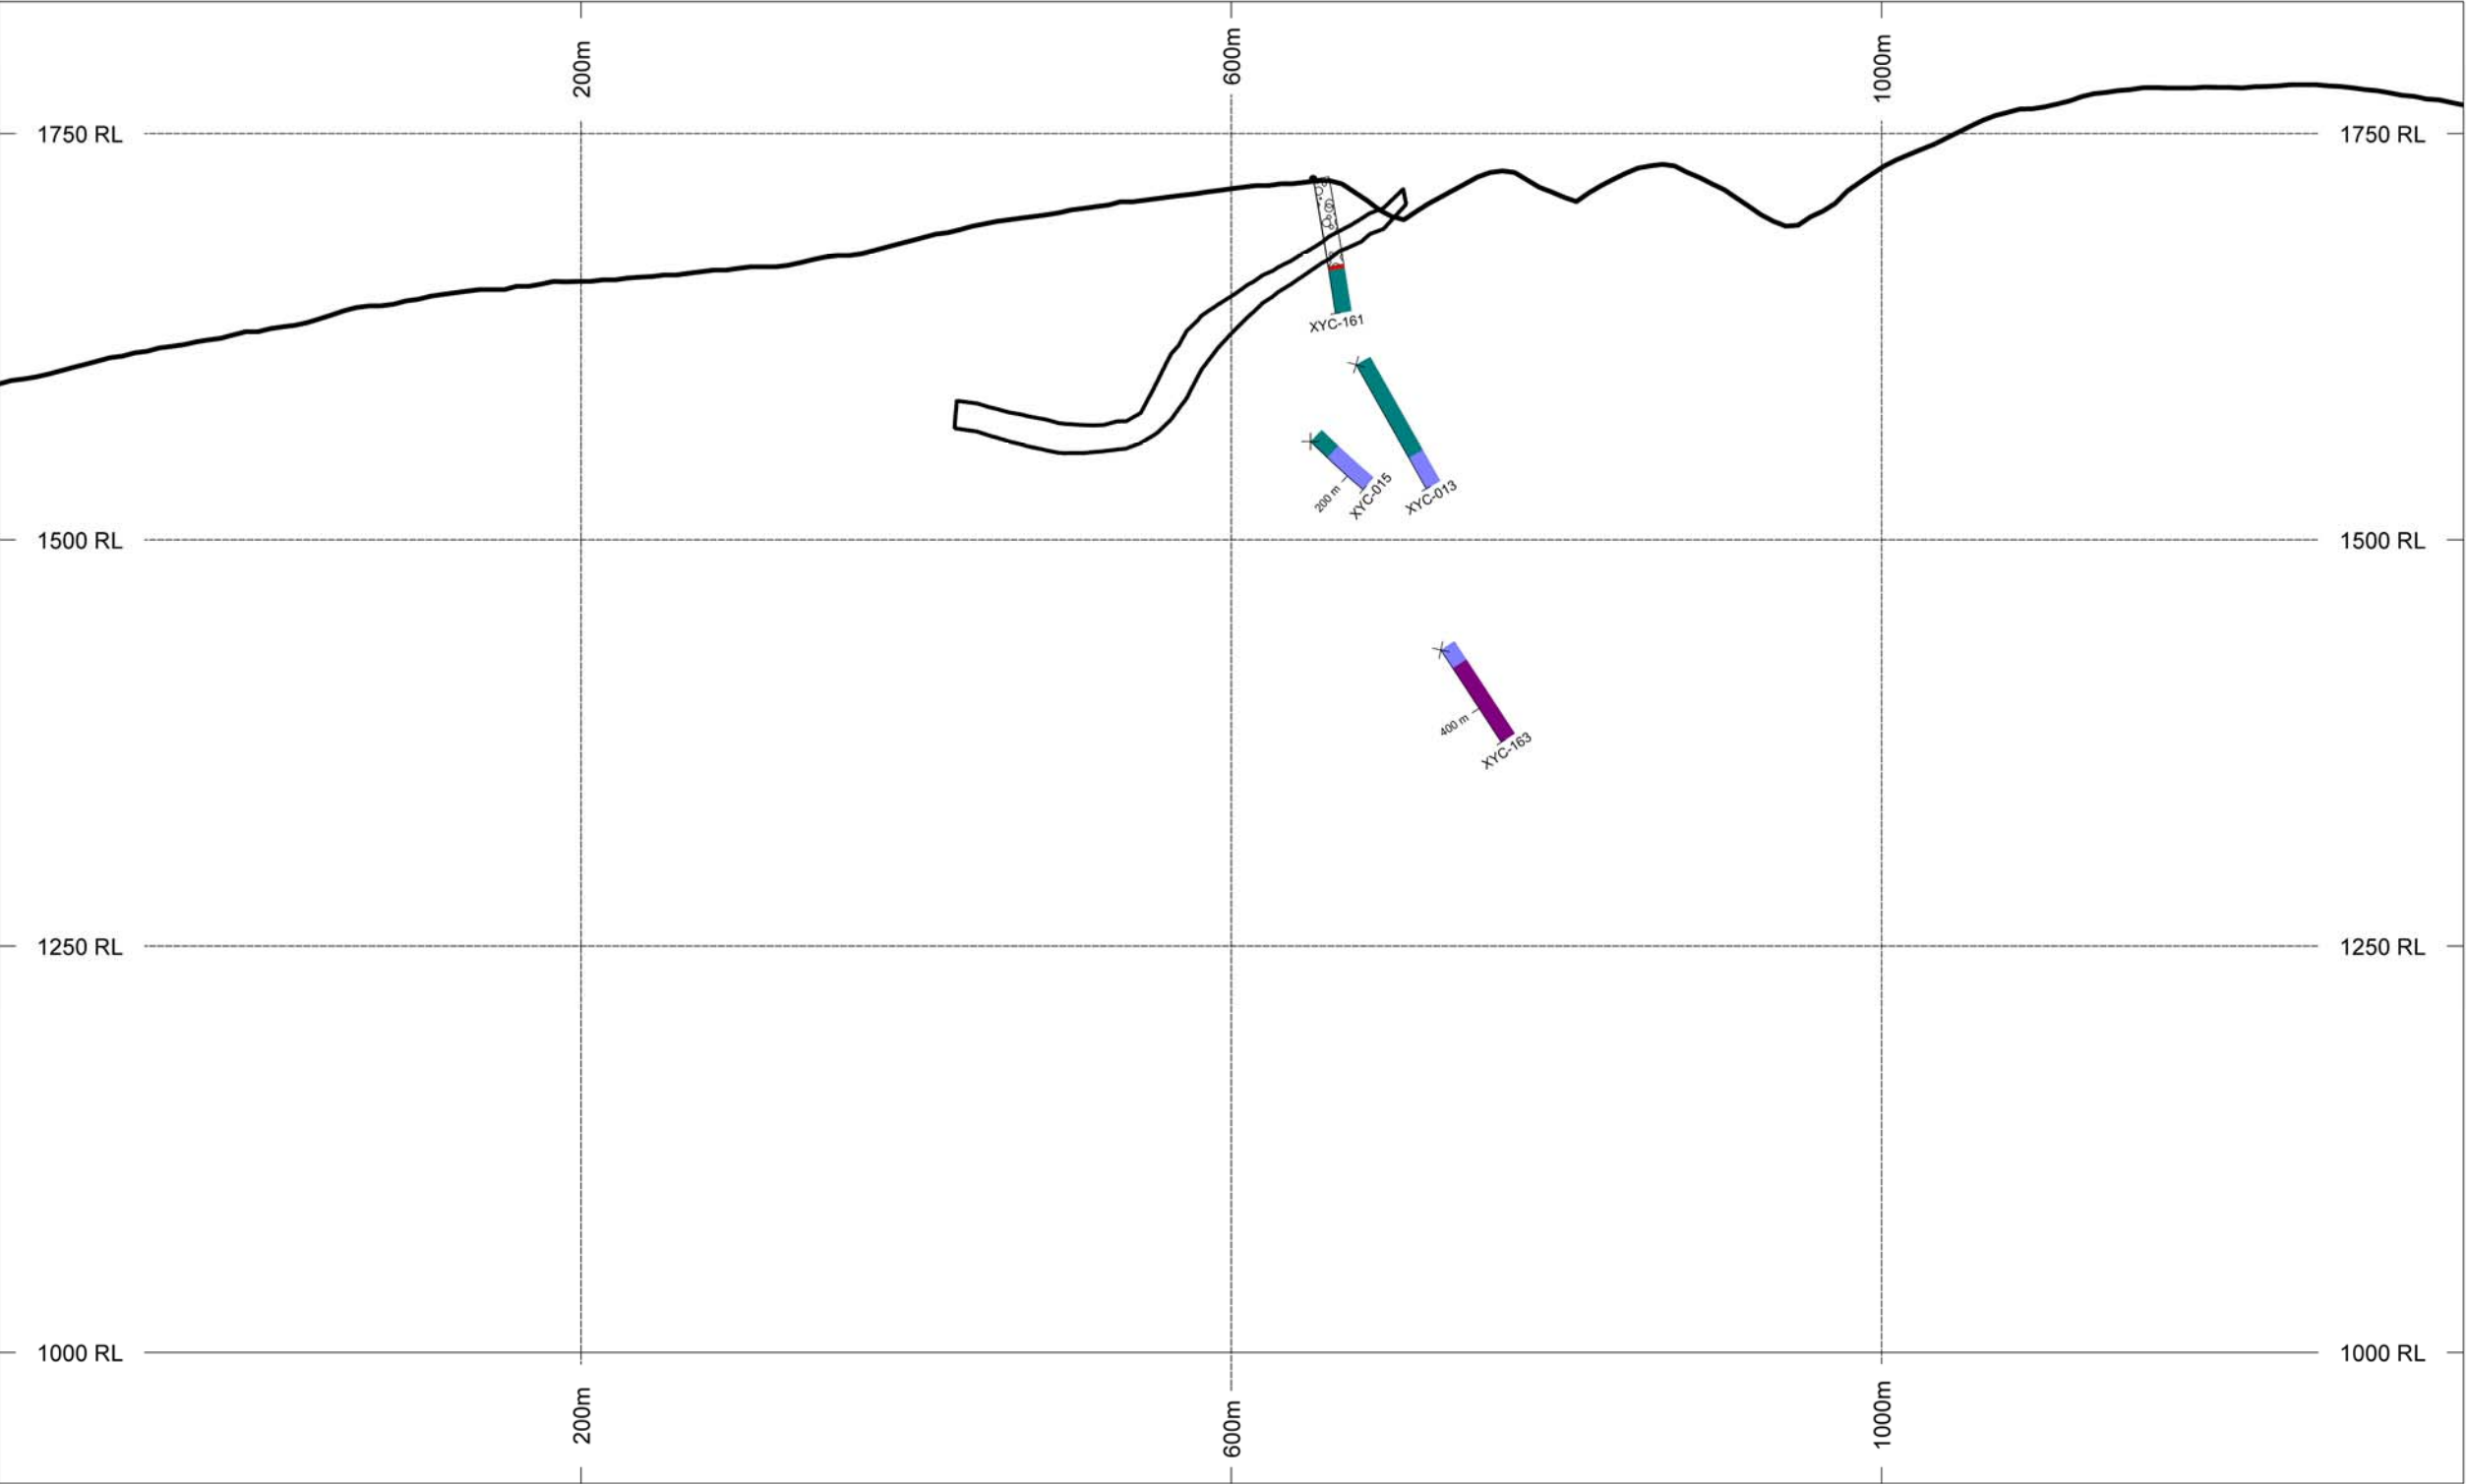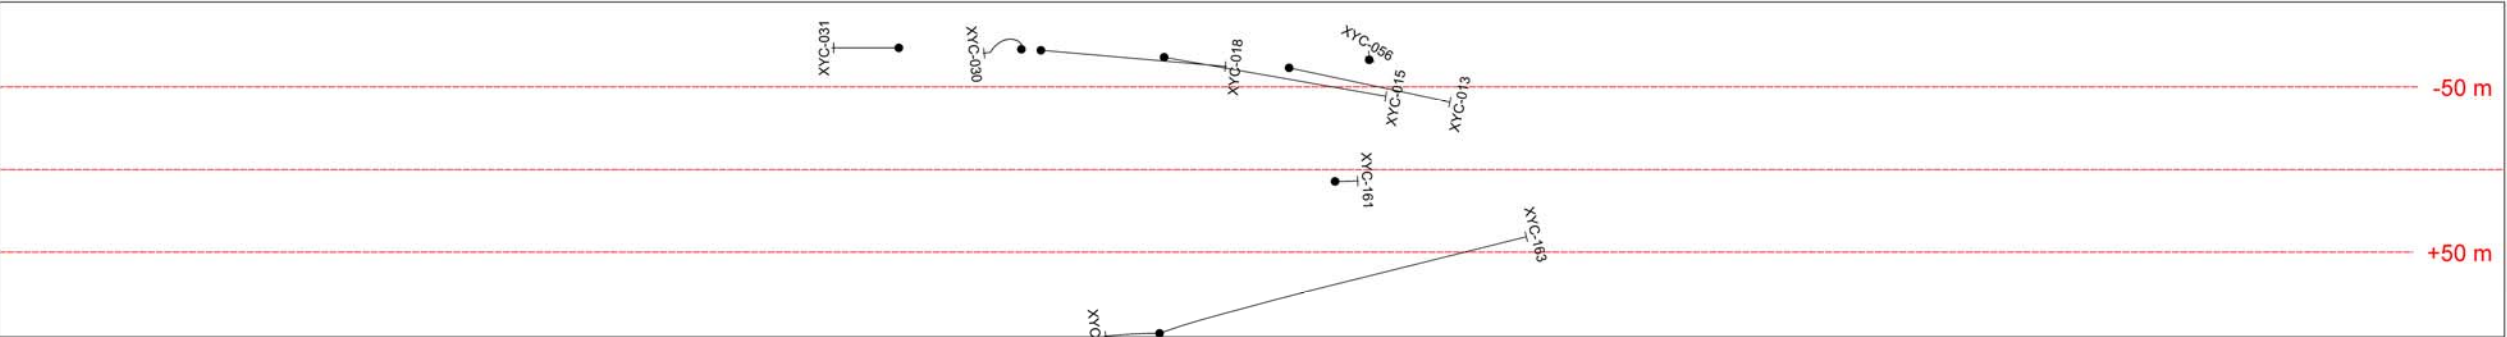

HOLES PLOTTED

TOTAL 4


XYC-013 XYC-015 XYC-161 XYC-163





ROCK CODES	PAT	LABEL	DESCRIPTION
rocktype			
		FLMD	Flaggy Mudstone
		USMS	Upper Siliceous Mudstone
		ACTM	Active Member
		LCMS	Lower Cherty Mudstone
		CCMS	Calcareous Mudstone
		PSMS	Pyritic Mudstone
		TRAN	Transition Formation
		CLST	Cambrian Limestone
		OVBR	Overburden
		FLT	Fault
		MDST	Undefined Mudstone

SECTION SPECS:

REF. PT. E, N	490078 m	6925878 m
EXTENTS	1516 m	911.9 m
SECTION TOP, BOT	1831 m	919.3 m
TOLERANCE +/-	50 m	

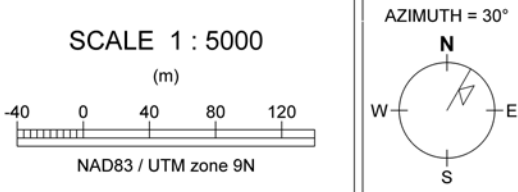

Selwyn Chihong Mining Ltd.
Selwyn Project, YT
Section L_01100N/0600E
XY Central Deposit

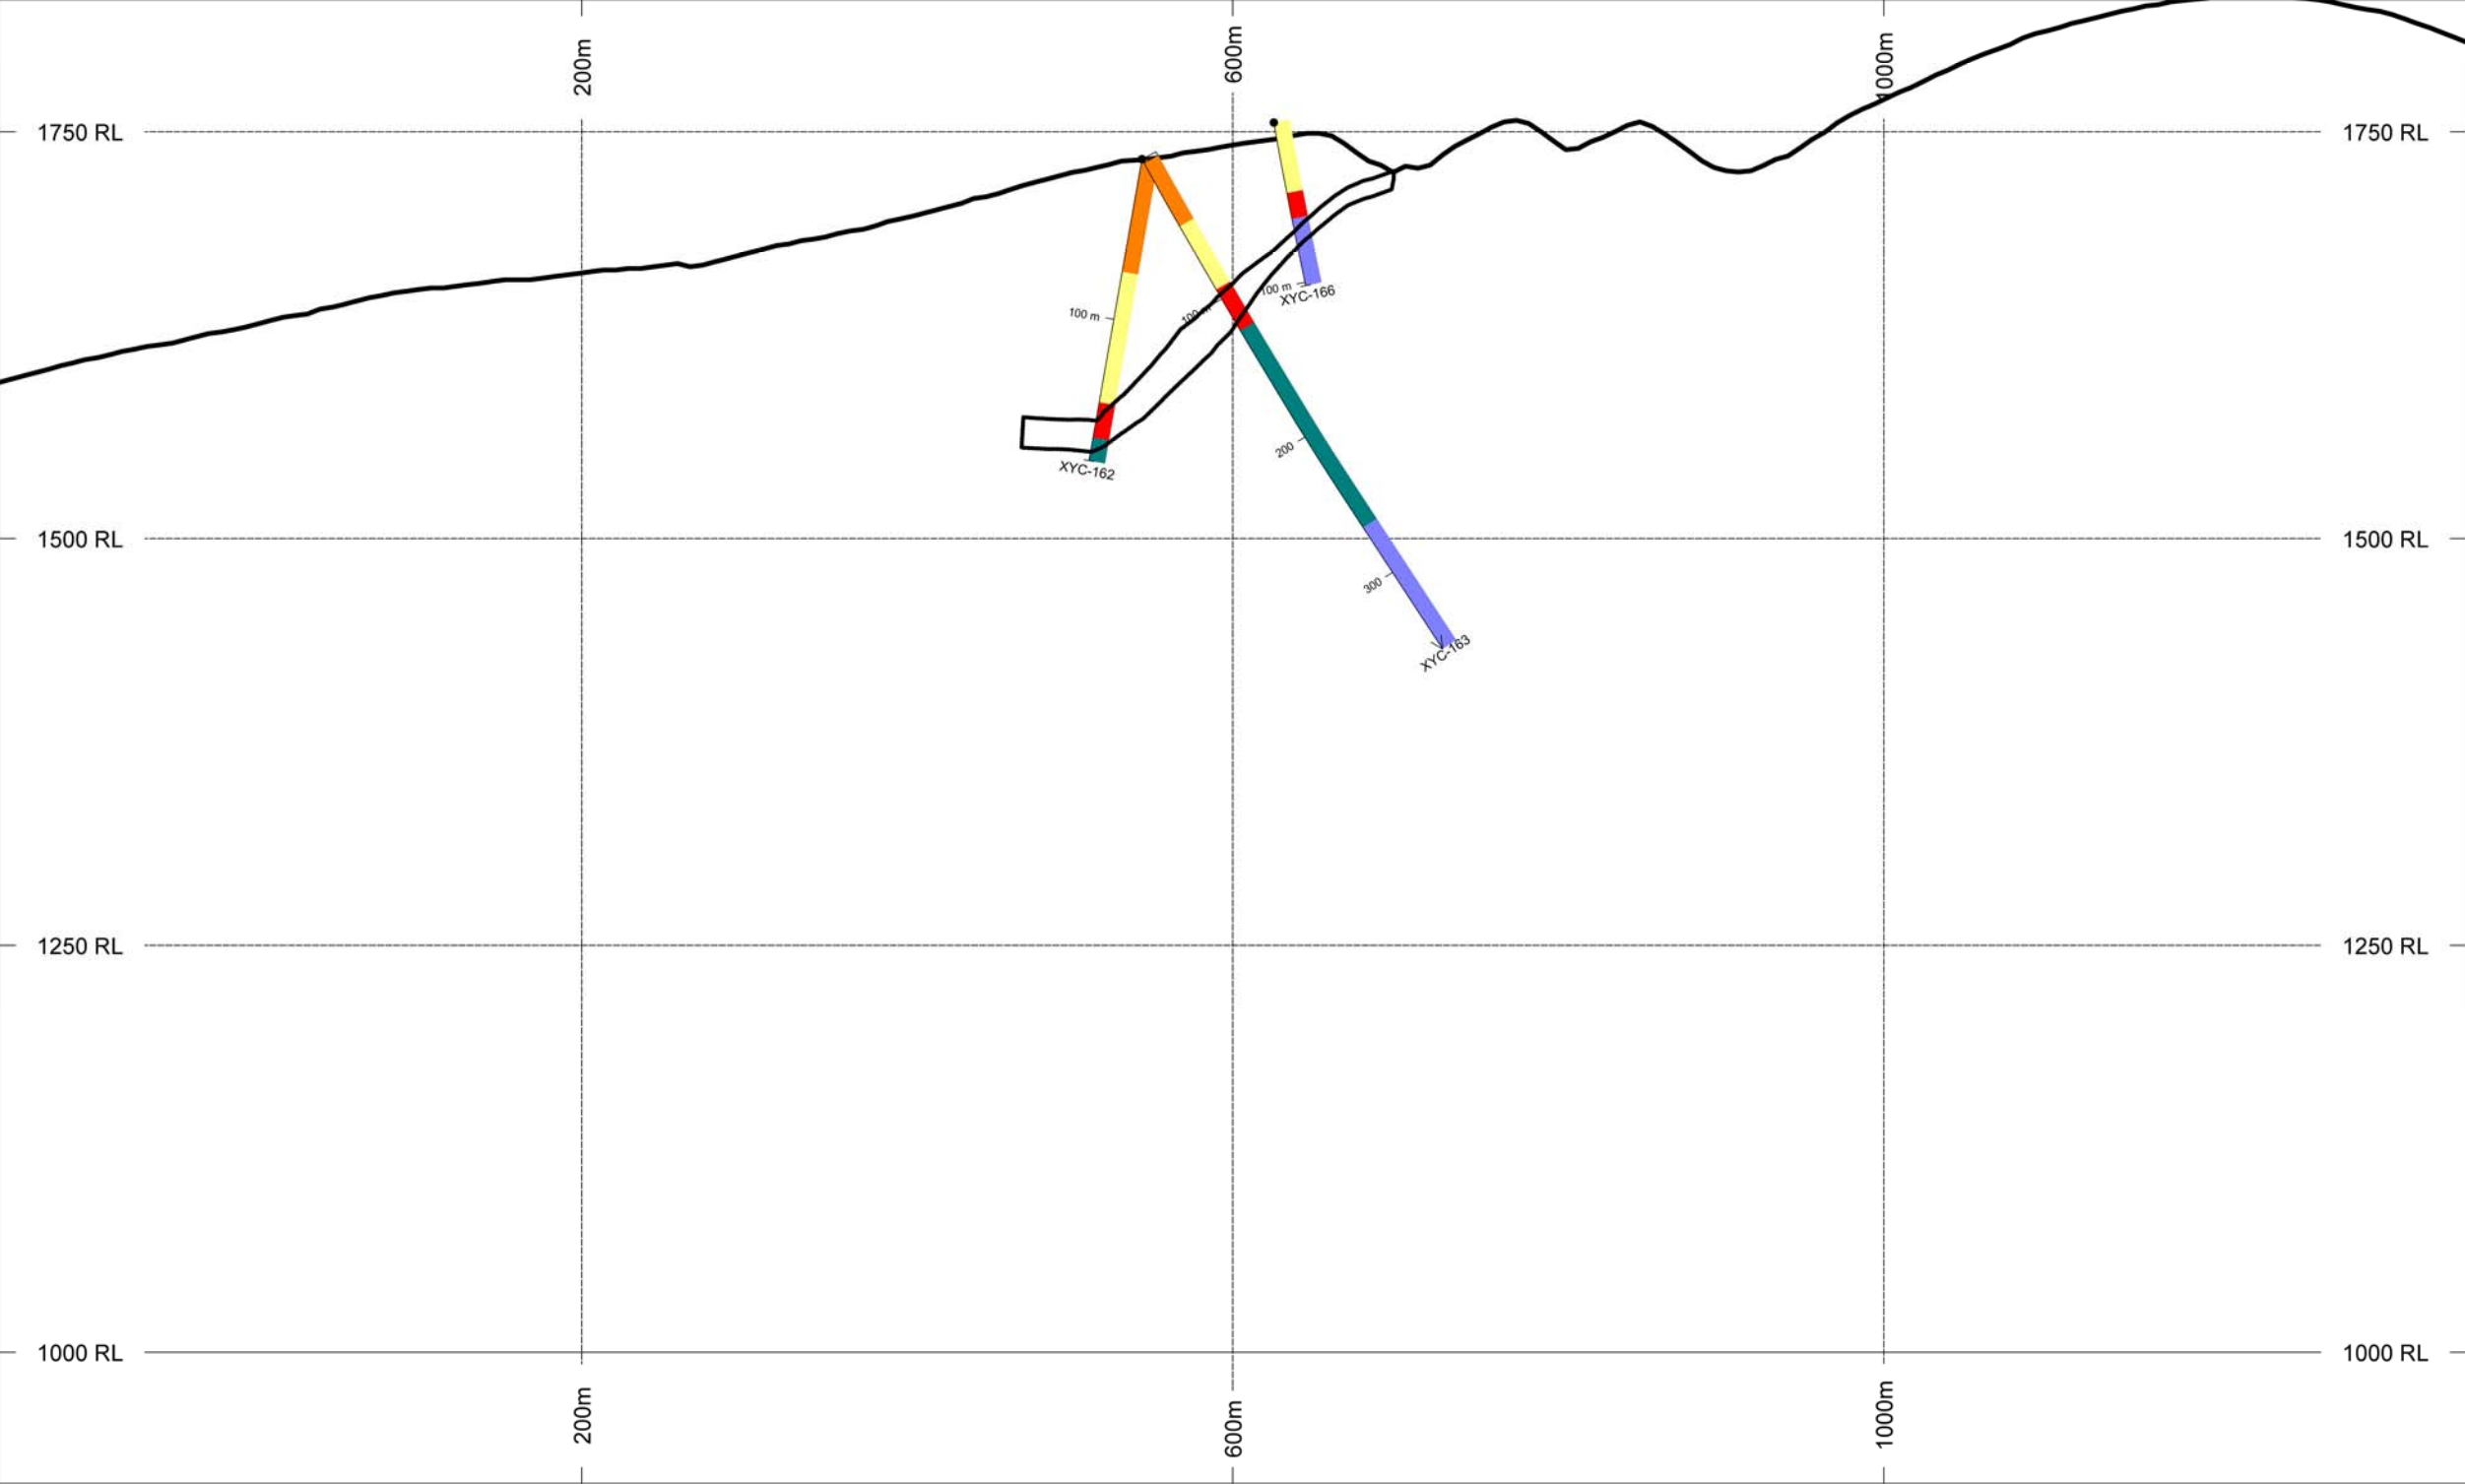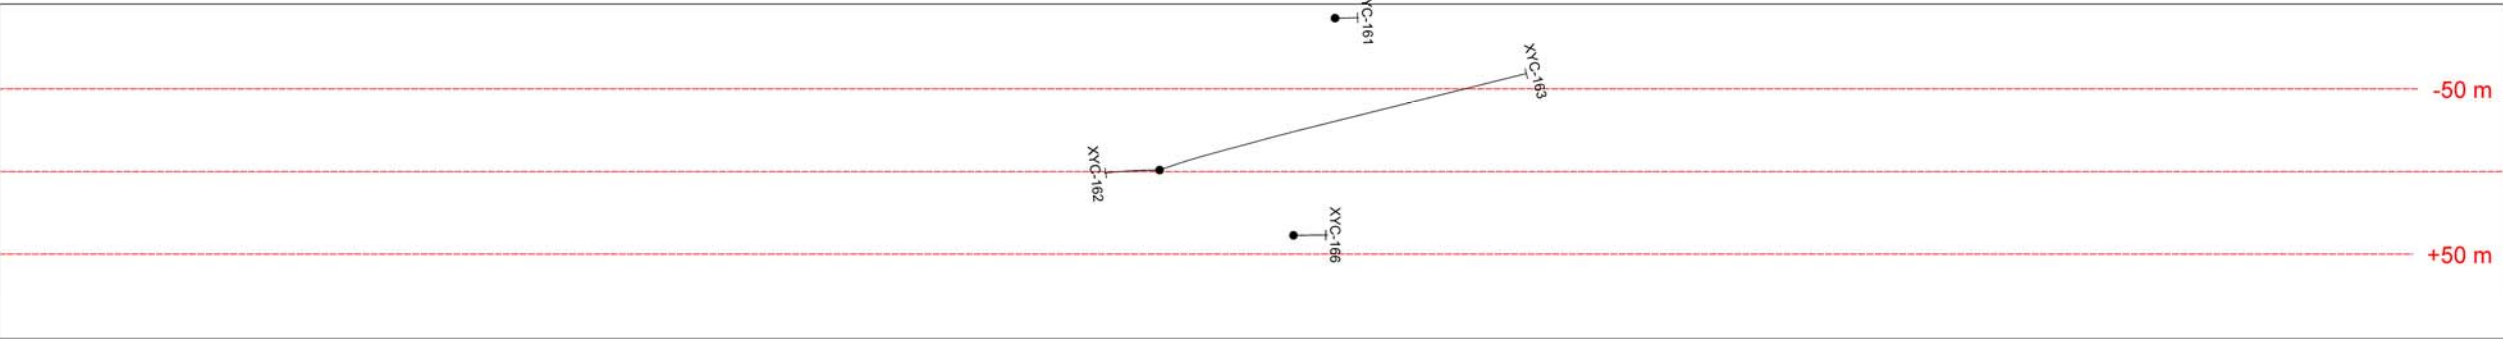

HOLES PLOTTED

TOTAL 3


XYC-162 XYC-163 XYC-166





ROCK CODES	PAT	LABEL	DESCRIPTION
rocktype			
		FLMD	Flaggy Mudstone
		USMS	Upper Siliceous Mudstone
		ACTM	Active Member
		LCMS	Lower Cherty Mudstone
		CCMS	Calcareous Mudstone
		PSMS	Pyritic Mudstone
		TRAN	Transition Formation
		CLST	Cambrian Limestone
		OVBR	Overburden
		FLT	Fault
		MDST	Undefined Mudstone

SECTION SPECS:

REF. PT. E, N	490165 m	6925828 m
EXTENTS	1516 m	911.9 m
SECTION TOP, BOT	1831 m	919.3 m
TOLERANCE +/-	50 m	

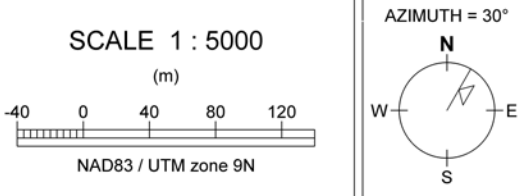

Selwyn Chihong Mining Ltd.
Selwyn Project, YT
Section L_01000N/0600E
XY Central Deposit

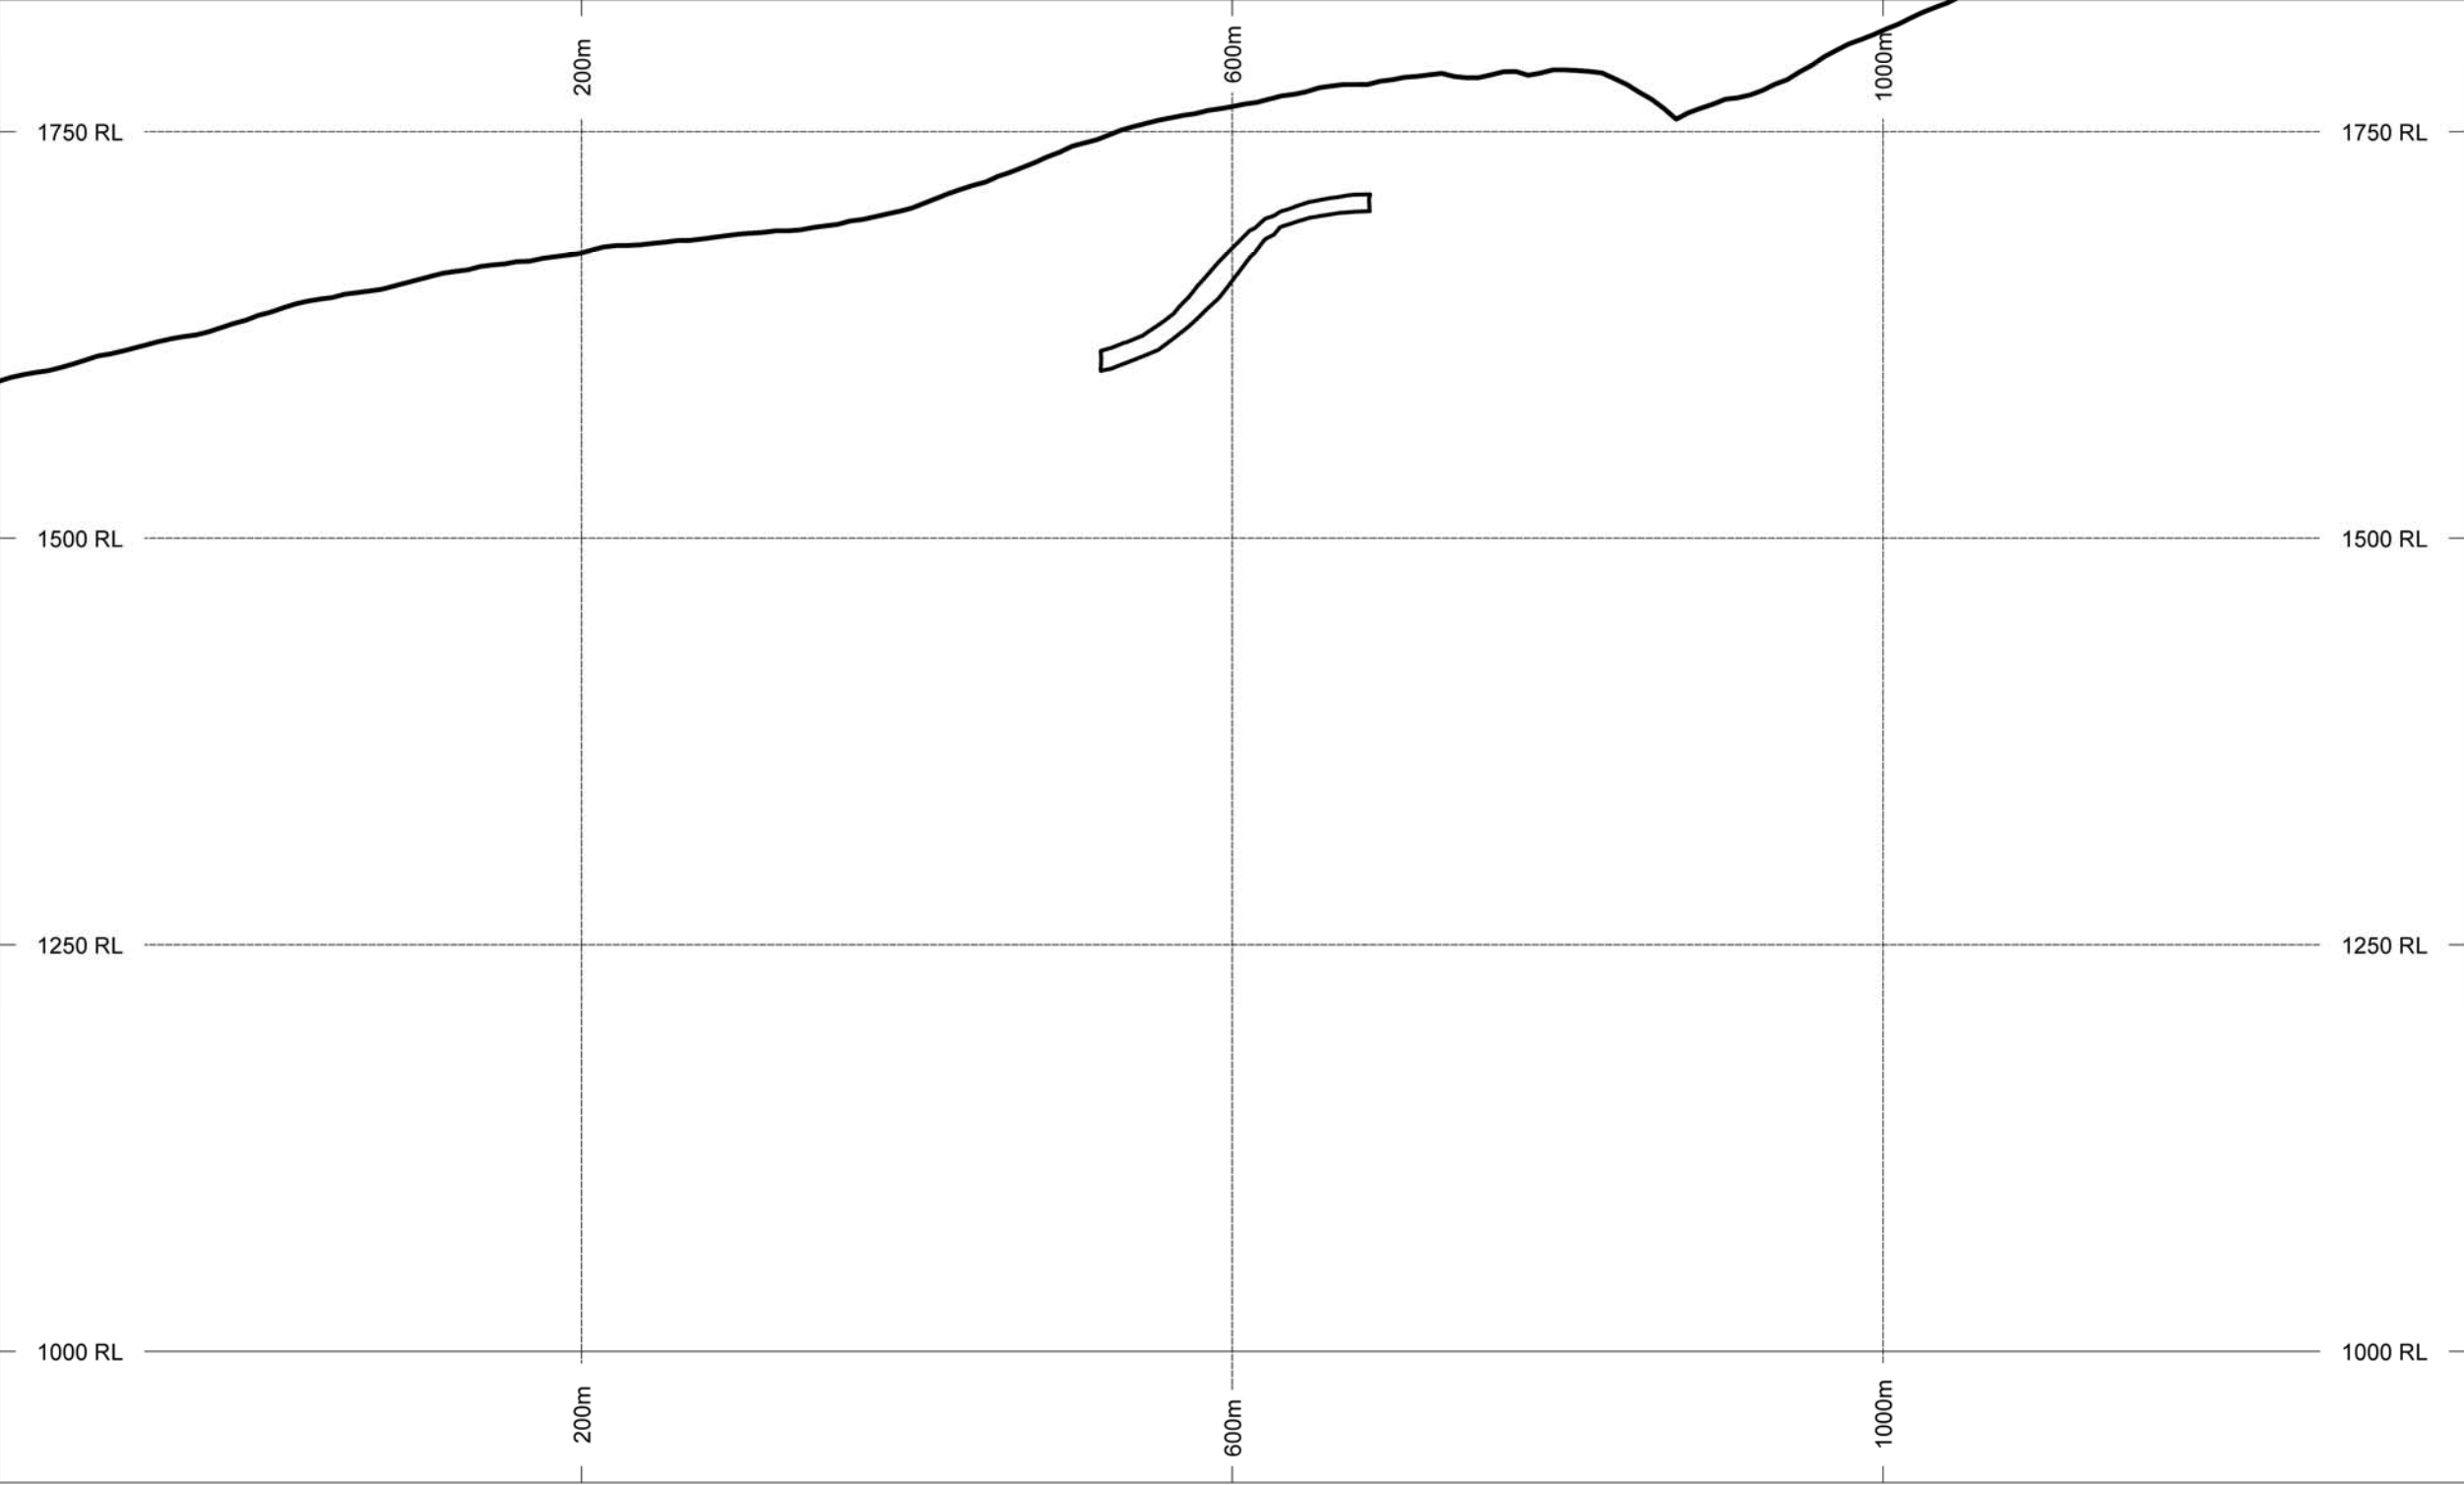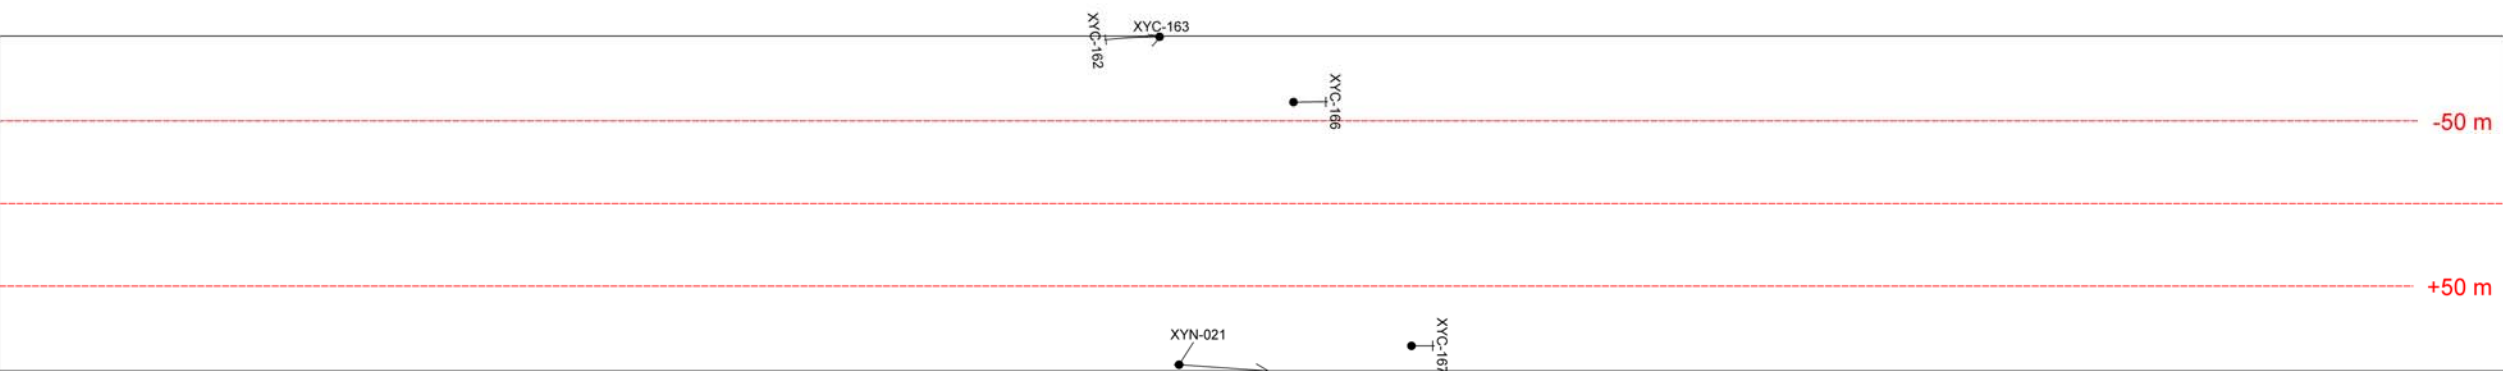

HOLES PLOTTED


TOTAL 0





ROCK CODES rocktype	PAT	LABEL	DESCRIPTION
		FLMD	Flaggy Mudstone
		USMS	Upper Siliceous Mudstone
		ACTM	Active Member
		LCMS	Lower Cherty Mudstone
		CCMS	Calcareous Mudstone
		PSMS	Pyritic Mudstone
		CLST	Cambrian Limestone
		OVBR	Overburden
		FLT	Fault
		MDST	Undefined Mudstone

SECTION SPECS:

REF. PT. E, N	490251 m	6925778 m
EXTENTS	1516 m	911.9 m
SECTION TOP, BOT	1831 m	919.3 m
TOLERANCE +/-	50 m	

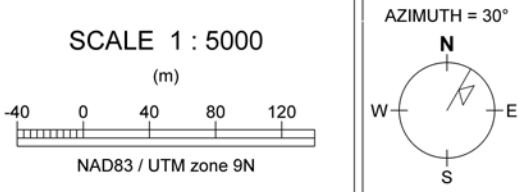

Selwyn Chihong Mining Ltd.
Selwyn Project, YT
Section L_00900N/0600E
XY Central Deposit

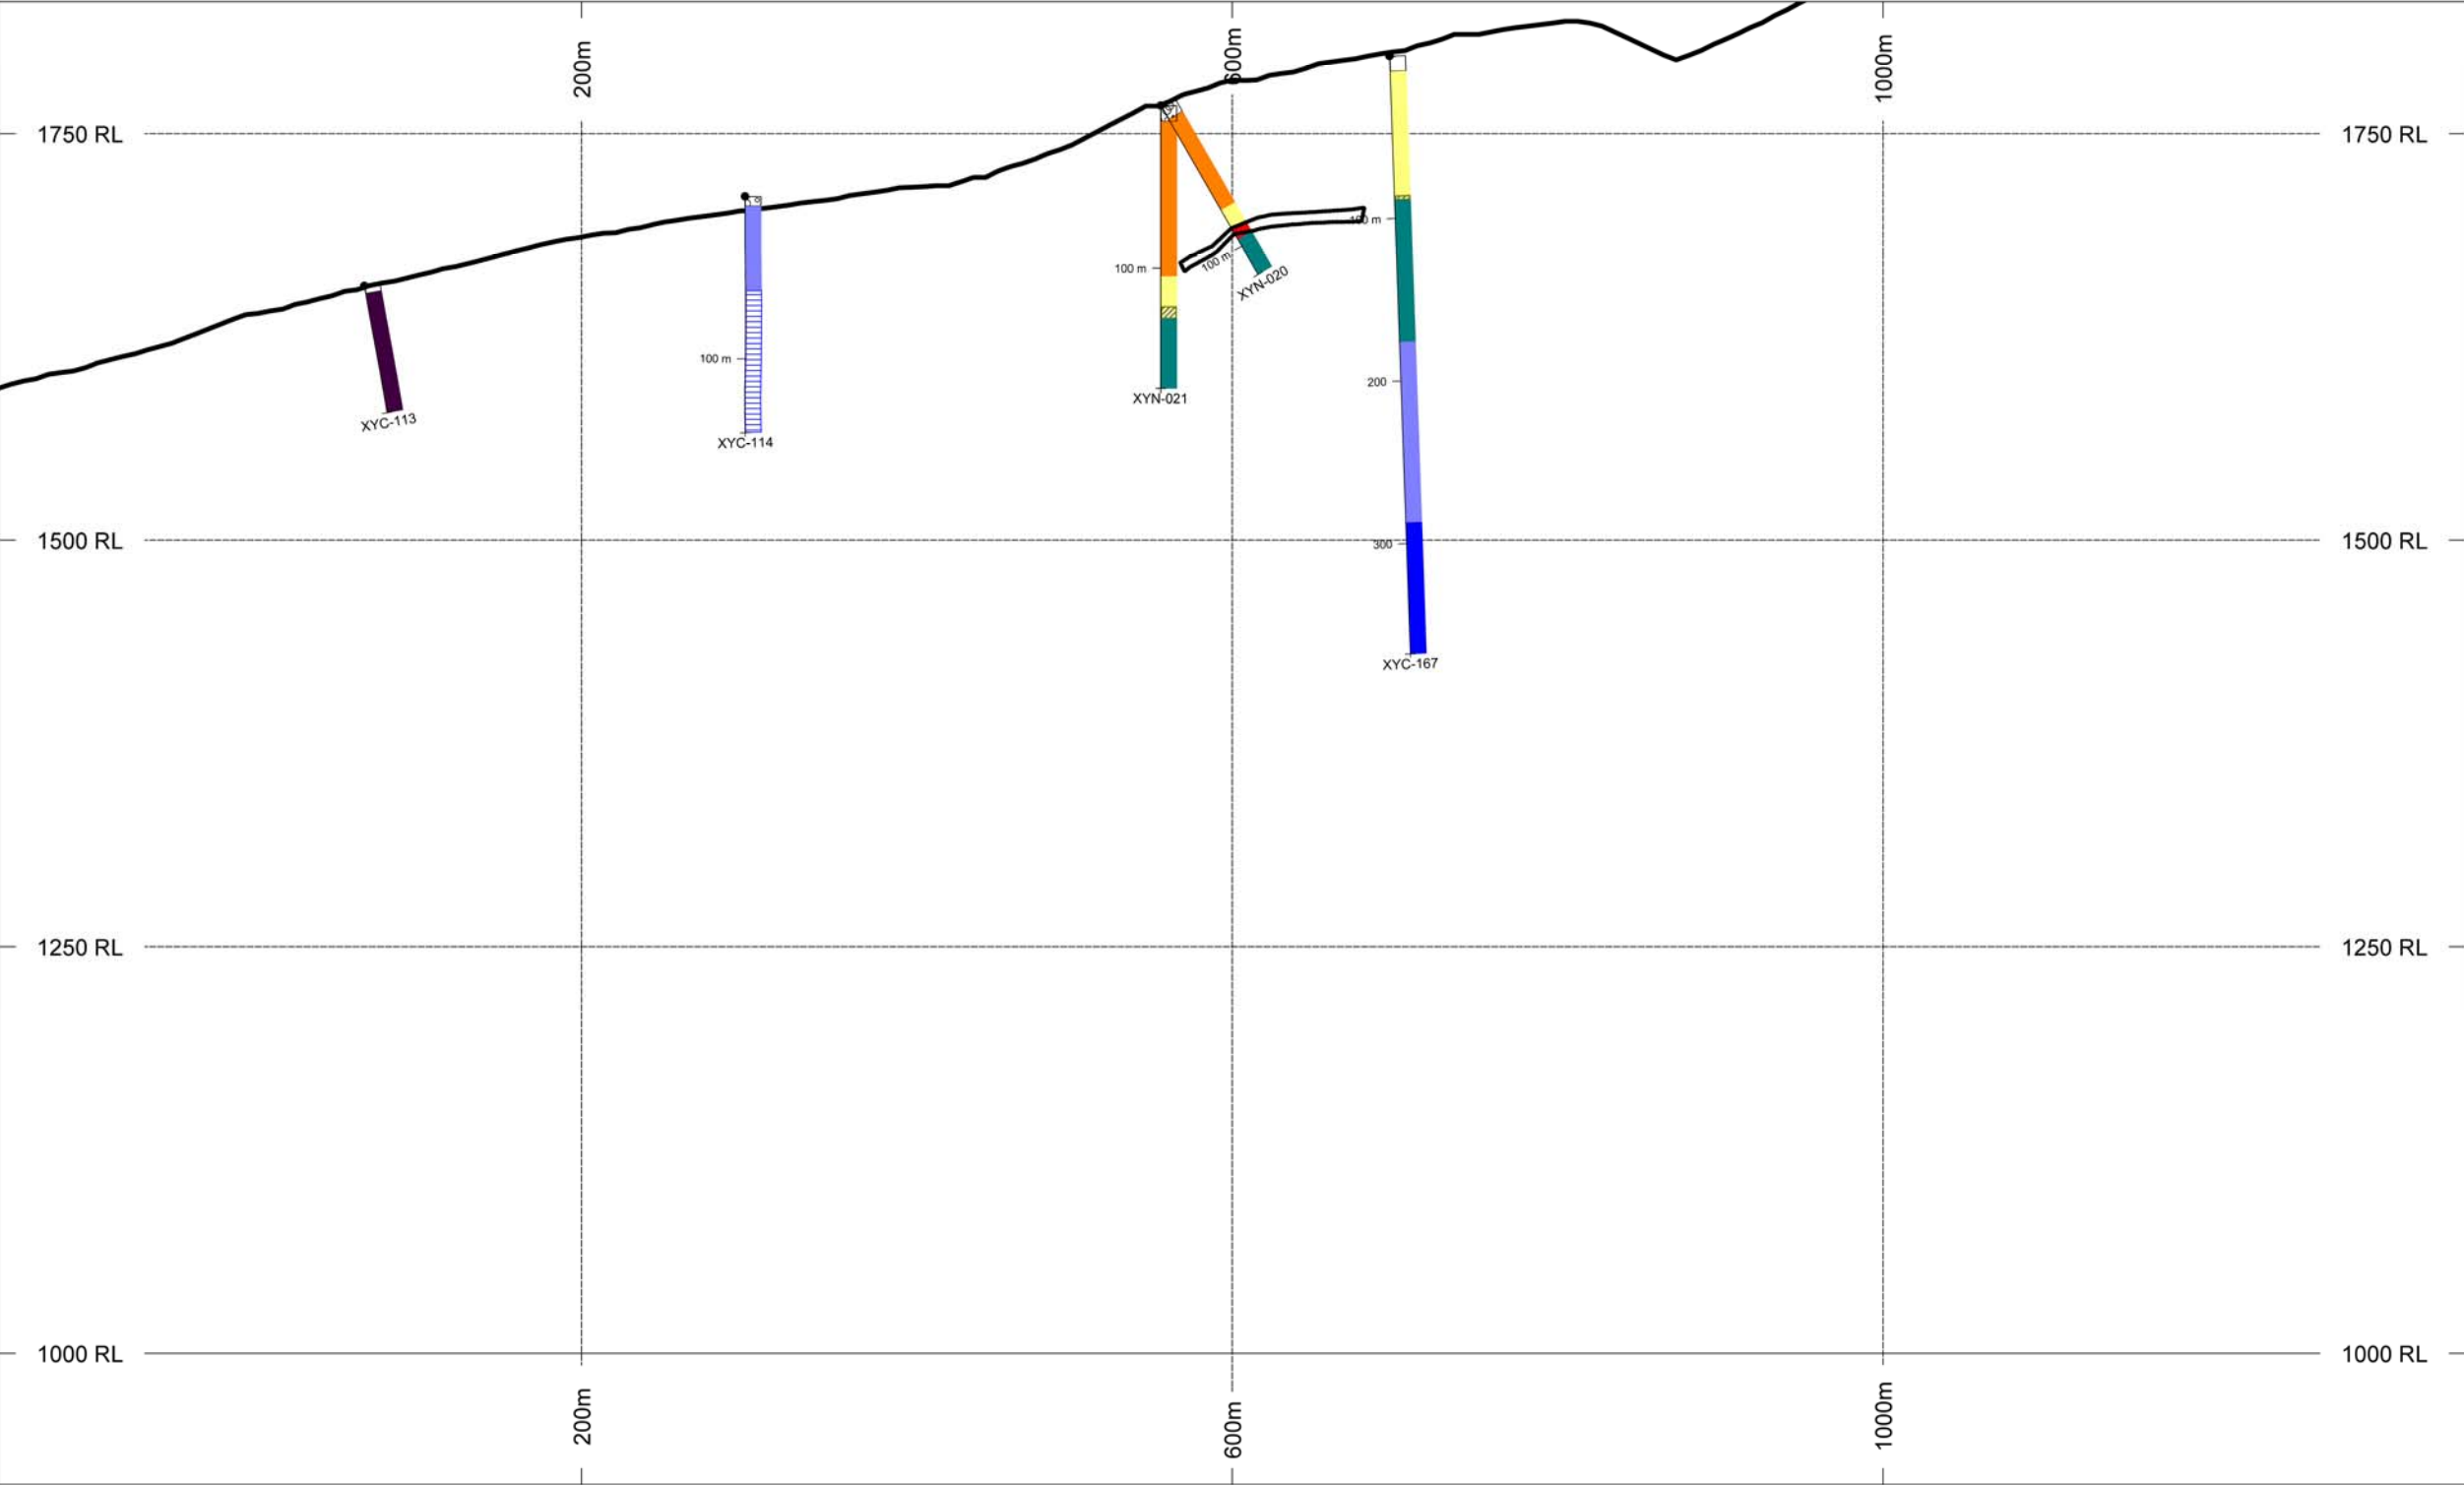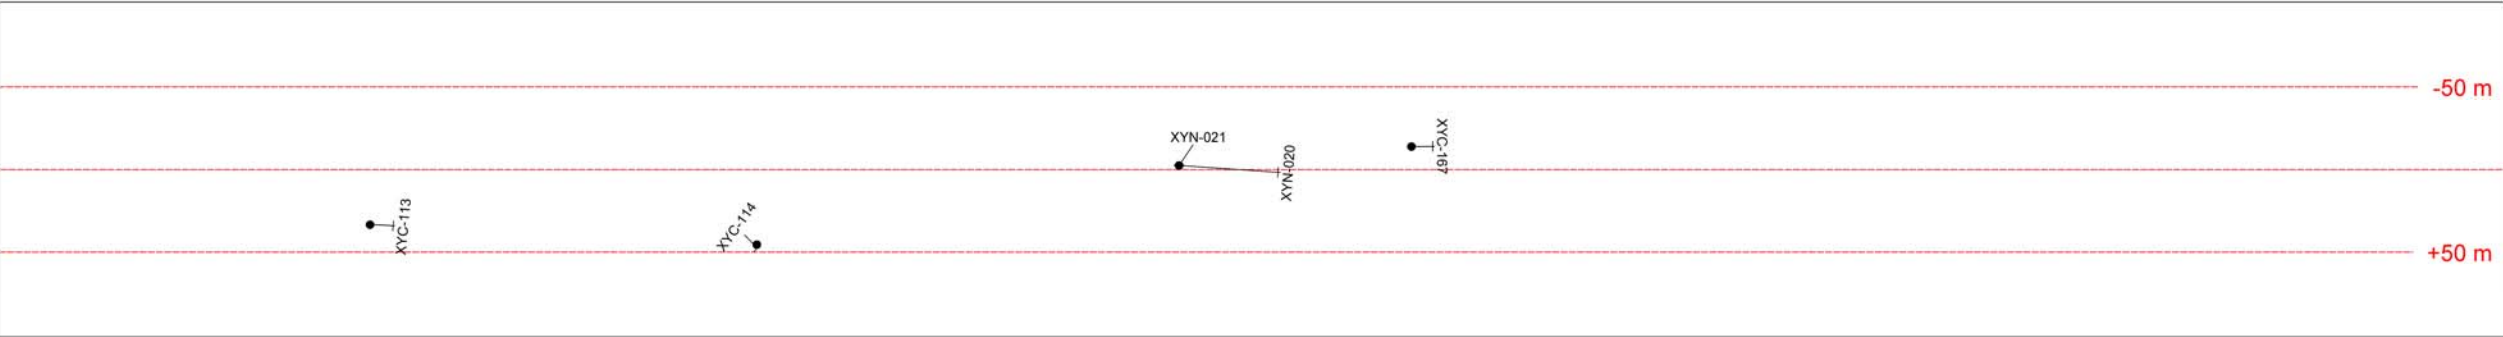

HOLES PLOTTED

TOTAL 5


XYC-113	XYC-114	XYC-167	XYN-020
XYN-021			



ROCK CODES	PAT	LABEL	DESCRIPTION
rocktype		FLMD	Flaggy Mudstone
		USMS	Upper Siliceous Mudstone
		ACTM	Active Member
		LCMS	Lower Cherty Mudstone
		CCMS	Calcareous Mudstone
		PSMS	Pyritic Mudstone
		CLST	Cambrian Limestone
		OVBR	Overburden
		FLT	Fault
		MDST	Undefined Mudstone

SECTION SPECS:

REF. PT. E, N	490338 m	6925728 m
EXTENTS	1516 m	911.9 m
SECTION TOP, BOT	1831 m	919.3 m
TOLERANCE +/-	50 m	

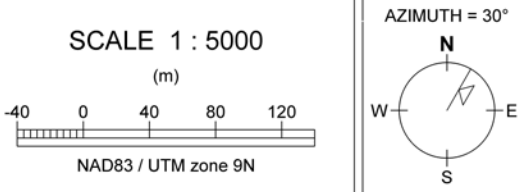

Selwyn Chihong Mining Ltd.
Selwyn Project, YT
Section L_00800N/0600E
XY Central Deposit



1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**

Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Submitted By: Jason K. Dunning

Receiving Lab: Canada-Whitehorse

Received: January 21, 2011

Report Date: January 31, 2011

Page: 1 of 3

CERTIFICATE OF ANALYSIS

WHI11000018.1

CLIENT JOB INFORMATION

Project: Selwyn Project
Shipment ID:
P.O. Number 1259
Number of Samples: 50

SAMPLE DISPOSAL

STOR-PLP Store After 90 days Invoice for Storage
STOR-RJT Store After 90 days Invoice for Storage

Acme does not accept responsibility for samples left at the laboratory after 90 days without prior written instructions for sample storage or return.

Invoice To: Selwyn Resources Ltd.
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6
Canada

CC:

SAMPLE PREPARATION AND ANALYTICAL PROCEDURES

Method Code	Number of Samples	Code Description	Test Wgt (g)	Report Status	Lab
R200-250	49	Crush split and pulverize 250g drill core to 200 mesh			WHI
7TD2	50	4 Acid digestion ICP-ES analysis.	0.5	Completed	VAN
G812	50	Specific Gravity on Pulp		Completed	VAN

ADDITIONAL COMMENTS



This report supersedes all previous preliminary and final reports with this file number dated prior to the date on this certificate. Signature indicates final approval; preliminary reports are unsigned and should be used for reference only.
All results are considered the confidential property of the client. Acme assumes the liabilities for actual cost of analysis only.
"*" asterisk indicates that an analytical result could not be provided due to unusually high levels of interference from other elements.



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: January 31, 2011

Page: 2 of 3 Part 1

CERTIFICATE OF ANALYSIS

WHI11000018.1

	Method Analyte Unit MDL	WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD
		Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg	Al
		kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%	%
		0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01	0.01
630701	Drill Core	1.56	<0.001	0.003	<0.02	0.09	<2	0.004	<0.001	<0.01	0.52	<0.02	<0.01	<0.001	<0.01	<0.01	1.21	0.27	0.004	0.07	0.73
630702	Drill Core	1.74	<0.001	0.002	<0.02	0.21	<2	0.004	<0.001	<0.01	0.55	<0.02	<0.01	<0.001	<0.01	<0.01	1.54	0.65	0.005	0.09	0.92
630703	Drill Core	1.13	0.002	0.006	0.18	0.29	2	0.012	<0.001	<0.01	1.44	<0.02	<0.01	<0.001	<0.01	<0.01	1.70	0.61	0.007	0.21	2.23
630704	Drill Core	1.81	<0.001	0.004	0.04	0.02	<2	0.003	<0.001	0.02	1.89	<0.02	<0.01	<0.001	<0.01	<0.01	9.31	0.24	0.004	0.08	0.71
630705	Drill Core	2.93	0.001	0.006	<0.02	0.14	<2	0.006	<0.001	<0.01	0.88	<0.02	<0.01	<0.001	<0.01	<0.01	3.47	1.15	0.006	0.11	1.41
630706	Drill Core	0.38	<0.001	0.003	<0.02	<0.01	<2	0.002	<0.001	0.06	1.31	<0.02	0.02	<0.001	<0.01	<0.01	27.44	0.20	<0.001	0.16	0.39
630707	Drill Core	0.43	0.001	0.003	<0.02	0.04	<2	0.006	<0.001	0.01	0.72	<0.02	<0.01	<0.001	<0.01	<0.01	6.45	0.61	0.004	0.11	1.25
630708	Drill Core	0.67	<0.001	0.009	0.04	<0.01	<2	0.002	<0.001	0.05	5.40	<0.02	0.01	<0.001	<0.01	<0.01	23.18	0.10	<0.001	0.07	0.18
630709	Drill Core	2.50	0.001	0.002	<0.02	0.24	<2	0.006	<0.001	<0.01	0.80	<0.02	<0.01	<0.001	<0.01	<0.01	2.05	0.77	0.004	0.09	1.13
630710	Drill Core	0.24	0.005	0.006	0.11	1.80	<2	0.009	<0.001	0.01	2.69	<0.02	<0.01	0.007	<0.01	<0.01	0.42	0.03	0.002	0.10	1.38
630711	Drill Core	0.32	0.005	0.005	0.13	1.64	<2	0.009	<0.001	0.01	2.68	<0.02	<0.01	0.006	<0.01	<0.01	3.08	0.04	0.003	0.11	1.40
630712	Drill Core	1.02	0.005	0.016	1.45	5.80	4	0.011	<0.001	0.02	10.09	<0.02	<0.01	0.018	<0.01	<0.01	2.83	0.06	0.003	0.10	1.53
630713	Drill Core	0.54	<0.001	0.007	2.61	9.23	<2	0.003	<0.001	<0.01	3.37	<0.02	<0.01	0.033	<0.01	<0.01	0.26	0.02	0.003	0.04	0.50
630714	Drill Core	1.80	0.004	0.009	1.99	5.43	<2	0.009	<0.001	0.02	8.06	<0.02	<0.01	0.019	<0.01	<0.01	1.18	0.05	0.004	0.08	1.19
630715	Drill Core	2.10	0.002	0.004	0.31	2.66	<2	0.005	<0.001	0.03	2.59	<0.02	<0.01	0.007	<0.01	<0.01	9.39	0.08	0.002	0.09	0.64
630716	Drill Core	2.81	<0.001	<0.001	0.17	0.04	<2	0.001	<0.001	0.07	0.38	<0.02	0.01	<0.001	<0.01	<0.01	27.57	0.02	<0.001	0.10	0.13
630717	Drill Core	2.15	0.001	0.001	0.07	0.02	<2	0.002	<0.001	0.01	0.85	<0.02	<0.01	<0.001	<0.01	<0.01	9.88	0.03	<0.001	0.05	0.34
630718	Drill Core	1.94	0.003	0.002	0.03	0.35	<2	0.008	<0.001	0.01	1.63	<0.02	<0.01	0.001	<0.01	<0.01	4.69	0.05	0.002	0.08	0.91
630719	Drill Core	1.96	0.008	0.023	2.06	13.84	<2	0.012	<0.001	0.04	10.19	<0.02	<0.01	0.039	<0.01	<0.01	1.69	0.04	0.002	0.08	1.27
630720	Rock	0.38	<0.001	<0.001	<0.02	0.01	<2	<0.001	<0.001	0.02	0.28	<0.02	0.01	<0.001	<0.01	<0.01	20.58	0.03	<0.001	10.82	0.48
630721	Drill Core	2.01	0.001	0.007	0.57	2.11	<2	0.003	<0.001	0.05	7.48	<0.02	<0.01	0.006	<0.01	<0.01	17.22	0.03	0.001	0.07	0.30
630722	Drill Core	1.09	<0.001	<0.001	<0.02	0.05	<2	<0.001	<0.001	0.05	0.22	<0.02	0.01	<0.001	<0.01	<0.01	29.60	0.02	<0.001	0.10	0.12
630723	Drill Core	3.28	<0.001	<0.001	0.04	0.18	<2	<0.001	<0.001	0.06	0.32	<0.02	0.01	<0.001	<0.01	<0.01	32.53	0.04	<0.001	0.10	0.17
630724	Drill Core	3.06	<0.001	0.002	0.64	2.33	<2	0.003	<0.001	0.02	1.34	<0.02	<0.01	0.008	<0.01	<0.01	2.95	0.07	0.001	0.05	0.34
630725	Drill Core	2.68	<0.001	0.002	1.09	1.37	<2	<0.001	<0.001	0.04	0.70	<0.02	0.01	0.004	<0.01	<0.01	22.26	0.16	<0.001	0.07	0.34
630726	Drill Core	2.60	0.001	0.003	1.44	3.37	<2	0.005	<0.001	0.03	1.78	<0.02	<0.01	0.011	<0.01	<0.01	10.97	0.09	0.002	0.10	0.85
630727	Drill Core	3.57	<0.001	0.001	1.12	3.98	<2	0.002	<0.001	0.04	1.35	<0.02	0.01	0.011	<0.01	<0.01	24.85	0.05	<0.001	0.09	0.38
630728	Drill Core	3.71	0.002	0.003	1.07	3.26	<2	0.004	<0.001	0.04	2.30	<0.02	0.01	0.010	<0.01	<0.01	19.56	0.07	0.001	0.10	0.70
630729	Drill Core	1.85	0.002	0.004	0.97	4.11	<2	0.005	<0.001	0.04	2.22	<0.02	<0.01	0.013	<0.01	<0.01	17.18	0.09	0.001	0.11	0.80
630730	Rock Pulp	0.06	<0.001	0.667	6.01	6.59	71	<0.001	<0.001	0.09	4.81	<0.02	0.02	0.018	0.04	<0.01	1.38	0.02	<0.001	0.25	5.36



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**

Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: January 31, 2011

Page: 2 of 3 Part 2

CERTIFICATE OF ANALYSIS

WHI11000018.1

	Method	7TD	7TD	7TD	7TD	G8SG
	Analyte	Na	K	W	S	SG
	Unit	%	%	%	%	
	MDL	0.01	0.01	0.01	0.05	0
630701	Drill Core	0.02	0.36	<0.01	0.27	2.51
630702	Drill Core	0.02	0.51	<0.01	0.50	2.49
630703	Drill Core	0.01	1.26	<0.01	1.61	2.41
630704	Drill Core	0.01	0.46	<0.01	2.08	2.61
630705	Drill Core	0.02	0.87	<0.01	0.77	2.45
630706	Drill Core	0.03	0.18	<0.01	1.46	2.63
630707	Drill Core	0.01	0.74	<0.01	0.68	2.38
630708	Drill Core	0.01	0.09	<0.01	6.42	2.70
630709	Drill Core	0.02	0.67	<0.01	0.76	2.38
630710	Drill Core	0.02	0.84	<0.01	3.76	2.38
630711	Drill Core	0.01	0.81	<0.01	3.73	2.44
630712	Drill Core	0.02	0.98	<0.01	14.10	2.68
630713	Drill Core	0.01	0.27	<0.01	8.43	2.72
630714	Drill Core	0.01	0.73	<0.01	11.68	2.69
630715	Drill Core	0.01	0.37	<0.01	4.11	2.56
630716	Drill Core	0.01	0.06	<0.01	0.44	2.56
630717	Drill Core	0.01	0.17	<0.01	0.82	2.49
630718	Drill Core	0.01	0.50	<0.01	1.77	2.40
630719	Drill Core	0.02	0.79	<0.01	17.64	2.84
630720	Rock	0.14	0.03	<0.01	0.05	2.65
630721	Drill Core	0.01	0.15	<0.01	9.40	2.77
630722	Drill Core	0.02	0.05	<0.01	0.28	2.51
630723	Drill Core	0.01	0.08	<0.01	0.41	2.52
630724	Drill Core	0.02	0.16	<0.01	2.48	2.56
630725	Drill Core	<0.01	0.14	<0.01	1.54	2.60
630726	Drill Core	0.01	0.50	<0.01	3.72	2.56
630727	Drill Core	0.01	0.16	<0.01	3.41	2.64
630728	Drill Core	0.01	0.34	<0.01	4.24	2.62
630729	Drill Core	0.01	0.42	<0.01	4.47	2.53
630730	Rock Pulp	2.24	1.37	<0.01	5.51	N.A.



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**

Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: January 31, 2011

Page: 3 of 3 Part 1

CERTIFICATE OF ANALYSIS

WHI11000018.1

	Method Analyte Unit MDL	WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	
		Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg	Al
		kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%	%
		0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01	0.01
630731	Drill Core	2.18	0.002	0.003	1.19	6.54	<2	0.005	<0.001	0.03	3.00	<0.02	<0.01	0.020	<0.01	<0.01	11.42	0.07	0.001	0.10	0.77
630732	Drill Core	3.14	<0.001	0.002	4.90	14.57	2	<0.001	<0.001	0.03	0.49	<0.02	<0.01	0.058	<0.01	<0.01	17.39	0.03	<0.001	0.04	0.16
630733	Drill Core	3.28	0.002	0.006	1.83	10.47	<2	0.007	<0.001	0.02	2.70	<0.02	<0.01	0.024	<0.01	<0.01	6.10	0.08	0.002	0.11	0.93
630734	Drill Core	2.68	<0.001	0.002	2.45	6.34	<2	0.003	<0.001	0.03	0.89	<0.02	<0.01	0.023	<0.01	<0.01	12.76	0.06	<0.001	0.07	0.41
630735	Drill Core	1.50	0.002	0.004	0.12	0.49	<2	0.007	<0.001	0.01	1.55	<0.02	<0.01	0.002	<0.01	<0.01	4.96	0.12	0.002	0.12	1.18
630736	Drill Core	1.88	0.002	0.004	0.66	1.07	<2	0.006	<0.001	0.02	1.85	<0.02	<0.01	0.005	<0.01	<0.01	12.73	0.06	0.002	0.11	0.93
630737	Drill Core	1.90	<0.001	0.002	0.14	<0.01	<2	0.002	<0.001	0.03	0.66	<0.02	0.01	0.002	<0.01	<0.01	17.08	0.03	<0.001	0.07	0.29
630738	Drill Core	0.88	<0.001	0.002	0.02	0.06	<2	0.003	<0.001	<0.01	0.75	<0.02	<0.01	<0.001	<0.01	<0.01	2.76	0.04	0.002	0.04	0.36
630739	Drill Core	2.07	0.003	0.006	0.47	2.91	<2	0.010	<0.001	<0.01	2.19	<0.02	<0.01	0.009	<0.01	<0.01	1.67	0.12	0.002	0.10	1.16
630740	Drill Core	0.53	0.002	0.004	0.53	1.40	<2	0.008	<0.001	0.02	1.29	<0.02	<0.01	0.004	<0.01	<0.01	8.79	0.08	0.002	0.11	1.07
630741	Drill Core	0.58	0.002	0.004	0.92	2.32	<2	0.007	<0.001	0.01	1.17	<0.02	<0.01	0.006	<0.01	<0.01	6.05	0.07	0.002	0.11	1.10
630742	Drill Core	3.09	0.001	0.003	0.30	0.26	<2	0.002	<0.001	0.03	0.46	<0.02	0.01	<0.001	<0.01	<0.01	24.14	0.05	<0.001	0.08	0.30
630743	Drill Core	3.20	<0.001	0.002	0.75	0.65	<2	0.002	<0.001	0.04	0.32	<0.02	0.02	0.002	<0.01	<0.01	29.88	0.06	<0.001	0.09	0.21
630744	Drill Core	0.67	<0.001	0.004	5.66	6.53	12	0.002	<0.001	<0.01	0.61	<0.02	<0.01	0.022	<0.01	<0.01	1.51	0.14	0.002	0.04	0.32
630745	Drill Core	1.03	0.001	0.005	0.50	3.18	<2	0.004	<0.001	0.04	1.15	<0.02	<0.01	0.013	<0.01	<0.01	12.61	0.25	0.001	0.09	0.35
630746	Drill Core	0.69	<0.001	0.002	<0.02	<0.01	<2	0.002	<0.001	0.09	0.48	<0.02	0.02	0.003	<0.01	<0.01	35.35	0.13	<0.001	0.21	0.09
630747	Drill Core	0.69	0.003	0.018	0.03	0.07	<2	0.010	<0.001	0.01	3.82	<0.02	<0.01	0.002	<0.01	<0.01	3.45	0.34	0.002	0.09	0.69
630748	Drill Core	3.08	0.005	0.016	<0.02	0.12	<2	0.009	<0.001	0.03	1.14	<0.02	0.02	0.003	<0.01	<0.01	23.60	2.31	0.003	0.11	0.42
630749	Drill Core	1.36	0.002	0.010	<0.02	0.04	<2	0.017	<0.001	0.01	3.17	<0.02	<0.01	<0.001	<0.01	<0.01	6.26	0.64	0.007	0.28	2.83
630750	Drill Core	1.32	0.001	0.012	<0.02	<0.01	<2	0.019	<0.001	<0.01	2.52	<0.02	<0.01	<0.001	<0.01	<0.01	2.26	0.49	0.011	0.31	4.44



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: January 31, 2011

Page: 3 of 3 **Part** 2

CERTIFICATE OF ANALYSIS

WHI11000018.1

	Method	7TD	7TD	7TD	7TD	G8SG
	Analyte	Na	K	W	S	SG
	Unit	%	%	%	%	
	MDL	0.01	0.01	0.01	0.05	0
630731	Drill Core	<0.01	0.44	<0.01	6.48	2.62
630732	Drill Core	0.01	0.08	<0.01	8.02	2.86
630733	Drill Core	<0.01	0.51	<0.01	8.95	2.65
630734	Drill Core	<0.01	0.23	<0.01	4.77	2.63
630735	Drill Core	<0.01	0.70	<0.01	2.04	2.39
630736	Drill Core	<0.01	0.54	<0.01	2.86	2.54
630737	Drill Core	<0.01	0.16	<0.01	0.76	2.51
630738	Drill Core	<0.01	0.18	<0.01	0.80	2.61
630739	Drill Core	<0.01	0.70	<0.01	3.90	2.49
630740	Drill Core	<0.01	0.65	<0.01	2.20	2.49
630741	Drill Core	<0.01	0.68	<0.01	2.61	2.61
630742	Drill Core	<0.01	0.16	<0.01	0.68	2.67
630743	Drill Core	<0.01	0.12	<0.01	0.81	2.57
630744	Drill Core	<0.01	0.18	<0.01	4.65	2.73
630745	Drill Core	<0.01	0.22	<0.01	2.93	2.63
630746	Drill Core	<0.01	0.11	<0.01	0.58	2.66
630747	Drill Core	<0.01	0.44	<0.01	4.04	2.57
630748	Drill Core	<0.01	0.22	<0.01	1.32	2.58
630749	Drill Core	<0.01	2.12	<0.01	3.51	2.43
630750	Drill Core	0.01	3.72	<0.01	2.76	2.47



Acme Analytical Laboratories (Vancouver) Ltd.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: Selwyn Resources Ltd.

Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: January 31, 2011

Page: 1 of 2 Part 1

QUALITY CONTROL REPORT

WHI11000018.1

	Method Analyte Unit MDL	WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	
		Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg	Al
		kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%	%
		0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01	0.01
Pulp Duplicates																					
630711	Drill Core	0.32	0.005	0.005	0.13	1.64	<2	0.009	<0.001	0.01	2.68	<0.02	<0.01	0.006	<0.01	<0.01	3.08	0.04	0.003	0.11	1.40
REP 630711	QC		0.006	0.005	0.13	1.61	<2	0.009	<0.001	0.01	2.66	<0.02	<0.01	0.006	<0.01	<0.01	3.06	0.04	0.003	0.11	1.38
630743	Drill Core	3.20	<0.001	0.002	0.75	0.65	<2	0.002	<0.001	0.04	0.32	<0.02	0.02	0.002	<0.01	<0.01	29.88	0.06	<0.001	0.09	0.21
REP 630743	QC		<0.001	0.002	0.73	0.65	<2	0.002	<0.001	0.04	0.32	<0.02	0.02	0.002	<0.01	<0.01	28.84	0.05	<0.001	0.09	0.21
630746	Drill Core	0.69	<0.001	0.002	<0.02	<0.01	<2	0.002	<0.001	0.09	0.48	<0.02	0.02	0.003	<0.01	<0.01	35.35	0.13	<0.001	0.21	0.09
REP 630746	QC		<0.001	0.002	<0.02	<0.01	<2	0.002	<0.001	0.09	0.53	<0.02	0.02	0.003	<0.01	<0.01	34.35	0.12	<0.001	0.20	0.09
Core Reject Duplicates																					
630705	Drill Core	2.93	0.001	0.006	<0.02	0.14	<2	0.006	<0.001	<0.01	0.88	<0.02	<0.01	<0.001	<0.01	<0.01	3.47	1.15	0.006	0.11	1.41
DUP 630705	QC		0.001	0.005	<0.02	0.14	<2	0.006	<0.001	<0.01	0.83	<0.02	<0.01	<0.001	<0.01	<0.01	3.54	1.16	0.007	0.11	1.41
630740	Drill Core	0.53	0.002	0.004	0.53	1.40	<2	0.008	<0.001	0.02	1.29	<0.02	<0.01	0.004	<0.01	<0.01	8.79	0.08	0.002	0.11	1.07
DUP 630740	QC		0.003	0.004	0.55	1.47	<2	0.008	<0.001	0.02	1.42	<0.02	<0.01	0.004	<0.01	<0.01	7.37	0.08	0.002	0.11	1.08
Reference Materials																					
STD OREAS131A	Standard		<0.001	0.032	1.72	2.90	30	0.002	0.002	0.17	5.81	<0.02	<0.01	0.008	<0.01	<0.01	5.34	0.06	0.002	3.18	4.72
STD OREAS131A	Standard		<0.001	0.032	1.70	2.87	31	0.003	0.002	0.18	5.78	<0.02	<0.01	0.008	<0.01	<0.01	5.19	0.06	0.002	3.19	4.72
STD OREAS131A	Standard		<0.001	0.032	1.71	2.77	30	0.003	0.002	0.17	5.87	<0.02	<0.01	0.010	<0.01	<0.01	5.31	0.06	0.002	3.13	4.62
STD R4T	Standard		0.064	0.512	1.56	3.49	87	0.353	0.040	0.09	24.20	<0.02	0.02	0.019	0.01	<0.01	2.19	0.05	0.018	1.44	4.01
STD R4T	Standard		0.062	0.514	1.52	3.42	90	0.352	0.040	0.09	24.28	<0.02	0.02	0.019	0.01	<0.01	2.20	0.05	0.018	1.42	3.97
STD R4T	Standard		0.063	0.516	1.52	3.41	86	0.352	0.041	0.09	24.06	<0.02	0.02	0.024	0.02	<0.01	2.15	0.04	0.019	1.42	3.95
STD SU-1B	Standard		<0.001	1.169	<0.02	0.02	6	1.951	0.066	0.07	24.88	<0.02	0.03	<0.001	<0.01	<0.01	2.20	0.06	0.031	1.78	4.38
STD SU-1B	Standard		<0.001	1.155	<0.02	0.02	6	1.982	0.065	0.07	25.23	<0.02	0.03	0.003	<0.01	<0.01	2.23	0.07	0.030	1.78	4.37
STD SU-1B	Standard		<0.001	1.170	<0.02	0.03	5	1.974	0.069	0.07	25.20	<0.02	0.03	0.004	<0.01	<0.01	2.22	0.06	0.032	1.79	4.38
STD R4T Expected			0.062	0.502	1.518	3.376	86	0.339	0.039	0.086	24.07	0.0087	0.0185	0.018	0.0138	0.0018	2.166	0.045	0.018	1.384	3.897
STD OREAS131A Expected			0.001	0.0322	1.72	2.83	30.9	0.0027	0.0023	0.1722	5.8166	0.0082	0.0028	0.0081	0.0047	0.001	5.286	0.0536	0.0025	3.1182	4.6057
STD SU-1B Expected			0.0004	1.185	0.0058	0.0235	6.4	1.97	0.0672	0.0703	25.54	0.00025	0.03	0.0003	0.00002	0.0003	2.21	0.06	0.032	1.79	4.39
BLK	Blank		<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	<0.01	<0.01	<0.02	<0.01	<0.001	<0.01	<0.01	<0.01	<0.01	<0.001	<0.01	<0.01
BLK	Blank		<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	<0.01	<0.01	<0.02	<0.01	<0.001	<0.01	<0.01	<0.01	<0.01	<0.001	<0.01	<0.01
BLK	Blank		<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	<0.01	<0.01	<0.02	<0.01	<0.001	<0.01	<0.01	<0.01	<0.01	<0.001	<0.01	<0.01
Prep Wash																					



Acme Analytical Laboratories (Vancouver) Ltd.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: Selwyn Resources Ltd.

Suite 700 - 509 Richards Street

Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: January 31, 2011

Page: 1 of 2 **Part** 2

QUALITY CONTROL REPORT

WHI11000018.1

Method		7TD	7TD	7TD	7TD	G8SG
Analyte		Na	K	W	S	SG
Unit		%	%	%	%	%
MDL		0.01	0.01	0.01	0.05	0
Pulp Duplicates						
630711	Drill Core	0.01	0.81	<0.01	3.73	2.44
REP 630711	QC	0.01	0.80	<0.01	3.61	
630743	Drill Core	<0.01	0.12	<0.01	0.81	2.57
REP 630743	QC	<0.01	0.12	<0.01	0.74	
630746	Drill Core	<0.01	0.11	<0.01	0.58	2.66
REP 630746	QC	<0.01	0.06	<0.01	0.54	
Core Reject Duplicates						
630705	Drill Core	0.02	0.87	<0.01	0.77	2.45
DUP 630705	QC	0.02	0.88	<0.01	0.80	2.43
630740	Drill Core	<0.01	0.65	<0.01	2.20	2.49
DUP 630740	QC	<0.01	0.65	<0.01	2.29	2.46
Reference Materials						
STD OREAS131A	Standard	0.16	3.43	<0.01	4.65	
STD OREAS131A	Standard	0.16	2.23	<0.01	4.76	
STD OREAS131A	Standard	0.15	3.35	<0.01	4.76	
STD R4T	Standard	0.93	1.19	<0.01	12.76	
STD R4T	Standard	0.93	1.17	<0.01	12.67	
STD R4T	Standard	0.91	1.18	<0.01	11.70	
STD SU-1B	Standard	1.66	0.61	<0.01	8.14	
STD SU-1B	Standard	1.69	0.61	<0.01	8.41	
STD SU-1B	Standard	1.67	0.62	<0.01	8.74	
STD R4T Expected		0.9	1.153	0.00016	12.9903	
STD OREAS131A Expected		0.1501	3.1584	0.0005	4.8	
STD SU-1B Expected		1.662	0.6	0.0007	8.76	
BLK	Blank	<0.01	<0.01	<0.01	<0.05	
BLK	Blank	<0.01	<0.01	<0.01	<0.05	
BLK	Blank	<0.01	<0.01	<0.01	<0.05	
Prep Wash						



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: January 31, 2011

Page: 2 of 2 **Part** 1

QUALITY CONTROL REPORT

WHI11000018.1

		WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	
		Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg	Al
		kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%	%
		0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01	0.01
G1	Prep Blank		<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	0.07	2.33	<0.02	0.08	<0.001	<0.01	<0.01	2.34	0.08	0.001	0.67	8.23
G1	Prep Blank		<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	0.08	2.44	<0.02	0.08	<0.001	<0.01	<0.01	2.44	0.08	0.002	0.70	8.21



Acme Analytical Laboratories (Vancouver) Ltd.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: **Selwyn Resources Ltd.**

Suite 700 - 509 Richards Street

Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: January 31, 2011

Page: 2 of 2 **Part** 2

QUALITY CONTROL REPORT

WHI11000018.1

		7TD Na %	7TD K %	7TD W %	7TD S %	G8SG SG
		0.01	0.01	0.01	0.05	0
G1	Prep Blank	2.70	1.94	<0.01	<0.05	2.63
G1	Prep Blank	2.67	2.21	<0.01	<0.05	2.63



1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: Selwyn Resources Ltd.

Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Submitted By: Jason K. Dunning

Receiving Lab: Canada-Whitehorse

Received: December 22, 2010

Report Date: January 10, 2011

Page: 1 of 4

CERTIFICATE OF ANALYSIS

WHI10000715.1

CLIENT JOB INFORMATION

Project: Selwyn Project
Shipment ID:
P.O. Number 1175
Number of Samples: 78

SAMPLE DISPOSAL

STOR-PLP Store After 90 days Invoice for Storage
STOR-RJT Store After 90 days Invoice for Storage

Acme does not accept responsibility for samples left at the laboratory after 90 days without prior written instructions for sample storage or return.

Invoice To: Selwyn Resources Ltd.
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6
Canada

CC:

SAMPLE PREPARATION AND ANALYTICAL PROCEDURES

Method Code	Number of Samples	Code Description	Test Wgt (g)	Report Status	Lab
R200-250	76	Crush split and pulverize 250g drill core to 200 mesh			WHI
7TD2	78	4 Acid digestion ICP-ES analysis.	0.5	Completed	VAN
G812	78	Specific Gravity on Pulp		Completed	VAN

ADDITIONAL COMMENTS



This report supersedes all previous preliminary and final reports with this file number dated prior to the date on this certificate. Signature indicates final approval; preliminary reports are unsigned and should be used for reference only.
All results are considered the confidential property of the client. Acme assumes the liabilities for actual cost of analysis only.
** asterisk indicates that an analytical result could not be provided due to unusually high levels of interference from other elements.



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: January 10, 2011

Page: 2 of 4 Part 1

CERTIFICATE OF ANALYSIS

WHI10000715.1

Method Analyte Unit MDL		WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD
		Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg	Al
		kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%	%
		0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.01	0.01	0.01
634051	Drill Core	1.17	<0.001	0.004	<0.02	<0.01	<2	0.009	<0.001	0.01	1.41	<0.02	<0.01	<0.001	<0.01	<0.01	8.32	1.36	0.006	0.14	1.35
634052	Drill Core	1.19	<0.001	0.001	<0.02	<0.01	<2	0.003	<0.001	0.06	0.54	<0.02	0.02	<0.001	<0.01	<0.01	33.60	0.27	<0.001	0.16	0.24
634053	Drill Core	0.76	<0.001	0.002	<0.02	0.12	<2	0.004	<0.001	0.01	0.61	<0.02	<0.01	<0.001	<0.01	<0.01	5.40	0.76	0.004	0.07	0.58
634054	Drill Core	2.29	<0.001	0.003	<0.02	0.11	<2	0.005	<0.001	0.02	0.94	<0.02	<0.01	<0.001	<0.01	<0.01	9.13	0.47	0.004	0.14	0.92
634055	Drill Core	2.14	0.001	0.004	<0.02	0.25	<2	0.007	<0.001	<0.01	0.98	<0.02	<0.01	<0.001	<0.01	<0.01	3.32	0.32	0.004	0.18	1.36
634056	Drill Core	1.12	0.002	0.006	0.16	0.28	<2	0.009	<0.001	0.01	2.00	<0.02	<0.01	<0.001	<0.01	<0.01	3.26	0.13	0.004	0.20	1.59
634057	Drill Core	1.68	<0.001	0.010	0.05	0.62	<2	0.007	<0.001	<0.01	3.53	<0.02	<0.01	0.002	<0.01	<0.01	1.34	0.35	0.003	0.10	0.79
634058	Drill Core	1.35	<0.001	0.003	<0.02	0.20	<2	0.006	<0.001	0.01	0.89	<0.02	<0.01	<0.001	<0.01	<0.01	3.57	0.46	0.004	0.12	1.08
634059	Drill Core	0.79	<0.001	0.006	<0.02	0.17	<2	0.009	<0.001	<0.01	1.21	<0.02	<0.01	<0.001	<0.01	<0.01	2.48	0.63	0.005	0.15	1.49
634060	Drill Core	0.21	<0.001	0.003	0.08	0.64	<2	0.004	<0.001	0.01	1.09	<0.02	<0.01	0.002	<0.01	<0.01	3.04	0.08	0.004	0.07	0.51
634061	Drill Core	0.27	0.001	0.003	0.31	0.85	<2	0.005	<0.001	<0.01	0.96	<0.02	<0.01	0.002	<0.01	<0.01	2.84	0.10	0.004	0.07	0.54
634062	Drill Core	1.87	<0.001	0.004	0.08	0.16	<2	0.007	<0.001	<0.01	1.10	<0.02	<0.01	<0.001	<0.01	<0.01	2.26	0.48	0.004	0.12	1.16
634063	Drill Core	2.38	<0.001	0.004	0.03	0.40	<2	0.007	<0.001	<0.01	1.11	<0.02	<0.01	0.001	<0.01	<0.01	3.05	0.76	0.005	0.12	1.20
634064	Drill Core	1.11	<0.001	0.002	<0.02	0.22	<2	0.005	<0.001	<0.01	0.79	<0.02	<0.01	<0.001	<0.01	<0.01	2.32	0.77	0.004	0.09	0.83
634065	Drill Core	0.63	<0.001	0.005	<0.02	<0.01	<2	0.003	<0.001	0.07	3.86	<0.02	0.02	<0.001	<0.01	<0.01	28.54	0.14	0.001	0.14	0.41
634066	Drill Core	1.39	0.003	0.012	0.03	0.16	2	0.014	<0.001	0.01	4.79	<0.02	<0.01	<0.001	<0.01	<0.01	2.76	0.73	0.006	0.21	2.08
634067	Drill Core	1.79	0.004	0.006	0.12	0.06	<2	0.009	<0.001	0.02	7.06	<0.02	<0.01	<0.001	<0.01	<0.01	9.02	0.05	0.003	0.12	1.08
634068	Drill Core	0.93	0.003	0.004	0.55	1.06	<2	0.007	<0.001	0.06	4.78	<0.02	0.01	0.003	<0.01	<0.01	17.19	0.09	0.003	0.13	0.62
634069	Drill Core	1.11	0.002	0.008	1.11	5.44	<2	0.006	<0.001	0.02	4.91	<0.02	<0.01	0.018	<0.01	<0.01	5.48	0.04	0.003	0.06	0.55
634070	Rock	0.39	<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	0.02	0.14	<0.02	<0.01	<0.001	<0.01	<0.01	20.96	0.04	<0.001	11.02	0.11
634071	Drill Core	1.85	0.003	0.009	2.69	5.16	3	0.010	<0.001	0.02	8.90	<0.02	<0.01	0.017	<0.01	<0.01	3.81	0.05	0.004	0.09	0.86
634072	Drill Core	1.05	0.003	0.008	0.28	2.78	<2	0.009	<0.001	0.02	4.28	<0.02	<0.01	0.010	<0.01	<0.01	7.04	0.04	0.003	0.11	0.81
634073	Drill Core	1.06	0.003	0.007	0.89	3.20	<2	0.010	<0.001	0.02	5.93	<0.02	<0.01	0.010	<0.01	<0.01	3.54	0.05	0.003	0.08	0.79
634074	Drill Core	1.10	0.003	0.004	0.05	0.27	<2	0.009	<0.001	0.03	4.13	<0.02	0.01	<0.001	<0.01	<0.01	15.17	0.05	0.002	0.10	0.75
634075	Drill Core	1.83	0.004	0.011	1.66	13.21	3	0.010	<0.001	0.03	5.61	<0.02	<0.01	0.041	<0.01	<0.01	7.09	0.05	0.003	0.08	0.71
634076	Drill Core	0.81	<0.001	<0.001	0.47	1.29	<2	0.002	<0.001	0.02	0.94	<0.02	0.01	0.004	<0.01	<0.01	13.00	0.02	0.001	0.04	0.24
634077	Drill Core	1.16	0.001	0.001	<0.02	0.24	<2	0.003	<0.001	<0.01	0.56	<0.02	<0.01	<0.001	<0.01	<0.01	2.61	0.03	0.003	0.04	0.41
634078	Drill Core	1.09	0.001	0.002	<0.02	0.11	<2	0.005	<0.001	<0.01	0.70	<0.02	<0.01	<0.001	<0.01	<0.01	1.15	0.04	0.003	0.05	0.44
634079	Drill Core	1.57	0.003	0.002	0.03	0.98	<2	0.009	<0.001	<0.01	0.96	<0.02	<0.01	0.003	<0.01	<0.01	4.28	0.06	0.004	0.09	1.01
634080	Rock Pulp	0.06	<0.001	0.477	1.37	2.99	18	<0.001	<0.001	0.45	2.69	<0.02	0.02	0.018	<0.01	<0.01	4.79	0.02	<0.001	0.33	4.16



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: January 10, 2011

Page: 2 of 4 **Part** 2

CERTIFICATE OF ANALYSIS

WHI10000715.1

	Method	7TD	7TD	7TD	7TD	G8SG
	Analyte	Na	K	W	S	SG
	Unit	%	%	%	%	
	MDL	0.01	0.01	0.01	0.05	0
634051	Drill Core	<0.01	0.85	<0.01	1.38	2.25
634052	Drill Core	0.01	0.13	<0.01	0.62	2.45
634053	Drill Core	<0.01	0.33	<0.01	0.49	2.36
634054	Drill Core	<0.01	0.54	<0.01	0.91	2.31
634055	Drill Core	<0.01	0.82	<0.01	1.09	2.30
634056	Drill Core	<0.01	0.93	<0.01	2.22	2.28
634057	Drill Core	<0.01	0.46	<0.01	4.12	2.46
634058	Drill Core	<0.01	0.64	<0.01	0.84	2.31
634059	Drill Core	<0.01	0.94	<0.01	1.27	2.27
634060	Drill Core	<0.01	0.28	<0.01	1.03	2.29
634061	Drill Core	<0.01	0.30	<0.01	1.23	2.30
634062	Drill Core	<0.01	0.72	<0.01	1.05	2.34
634063	Drill Core	<0.01	0.73	<0.01	1.24	2.35
634064	Drill Core	<0.01	0.48	<0.01	0.65	2.28
634065	Drill Core	<0.01	0.23	<0.01	4.47	2.53
634066	Drill Core	<0.01	1.20	<0.01	5.27	2.21
634067	Drill Core	<0.01	0.62	<0.01	7.89	2.39
634068	Drill Core	<0.01	0.46	<0.01	5.96	2.43
634069	Drill Core	<0.01	0.32	<0.01	7.97	2.55
634070	Rock	0.01	0.02	<0.01	0.07	2.58
634071	Drill Core	<0.01	0.48	<0.01	12.49	2.74
634072	Drill Core	<0.01	0.45	<0.01	6.03	2.44
634073	Drill Core	<0.01	0.46	<0.01	8.13	2.49
634074	Drill Core	<0.01	0.41	<0.01	4.73	2.49
634075	Drill Core	<0.01	0.42	<0.01	12.49	2.74
634076	Drill Core	<0.01	0.14	<0.01	1.62	2.51
634077	Drill Core	<0.01	0.21	<0.01	0.50	2.41
634078	Drill Core	<0.01	0.24	<0.01	0.49	2.33
634079	Drill Core	<0.01	0.62	<0.01	1.38	2.22
634080	Rock Pulp	1.68	1.26	<0.01	3.09	N.A.



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: January 10, 2011

Page: 3 of 4 Part 1

CERTIFICATE OF ANALYSIS

WHI10000715.1

	Method Analyte Unit MDL	WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD
		Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg
		kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%
		0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01
634081	Drill Core	0.72	0.008	0.003	0.02	0.50	<2	0.015	<0.001	<0.01	1.65	<0.02	<0.01	0.001	<0.01	<0.01	1.74	0.06	0.005	0.16
634082	Drill Core	0.87	0.007	0.007	0.64	5.77	<2	0.012	<0.001	0.02	3.42	<0.02	<0.01	0.015	<0.01	<0.01	7.68	0.04	0.003	0.12
634083	Drill Core	1.42	<0.001	0.004	0.60	4.68	<2	0.004	<0.001	0.05	1.85	<0.02	0.01	0.014	<0.01	<0.01	23.32	0.05	0.001	0.09
634084	Drill Core	2.54	0.002	0.003	0.68	3.78	<2	0.005	<0.001	0.02	1.58	<0.02	<0.01	0.010	<0.01	<0.01	10.87	0.05	0.002	0.09
634085	Drill Core	1.27	0.001	0.002	<0.02	0.31	<2	0.005	<0.001	<0.01	0.73	<0.02	<0.01	<0.001	<0.01	<0.01	3.35	0.04	0.002	0.05
634086	Drill Core	1.63	<0.001	0.002	<0.02	0.01	<2	0.002	<0.001	0.03	1.27	<0.02	0.02	<0.001	<0.01	<0.01	23.12	0.01	<0.001	0.09
634087	Drill Core	1.62	0.002	0.005	0.04	0.23	<2	0.006	<0.001	0.03	0.69	<0.02	0.01	<0.001	<0.01	<0.01	15.00	0.05	0.002	0.10
634088	Drill Core	1.55	0.001	0.003	<0.02	0.04	<2	0.005	<0.001	0.02	1.34	<0.02	<0.01	<0.001	<0.01	<0.01	8.39	0.04	0.002	0.07
634089	Drill Core	1.47	0.002	0.006	0.21	1.31	<2	0.007	<0.001	0.03	1.66	<0.02	0.01	0.003	<0.01	<0.01	11.45	0.26	0.003	0.09
634090	Drill Core	0.38	0.004	0.008	0.16	0.31	<2	0.009	<0.001	0.03	1.50	<0.02	0.01	<0.001	<0.01	<0.01	13.10	0.17	0.002	0.11
634091	Drill Core	0.43	0.003	0.005	0.16	1.15	<2	0.009	<0.001	0.02	1.25	<0.02	<0.01	0.002	<0.01	<0.01	9.31	0.35	0.003	0.09
634092	Drill Core	1.33	0.002	0.011	0.13	0.05	<2	0.006	<0.001	0.03	2.82	<0.02	0.02	<0.001	<0.01	<0.01	23.22	4.12	0.002	0.06
634093	Drill Core	1.37	0.001	0.002	<0.02	<0.01	<2	0.004	<0.001	0.03	0.45	<0.02	0.02	<0.001	<0.01	<0.01	14.90	0.14	0.002	0.07
634094	Drill Core	2.39	0.002	0.003	0.76	3.10	<2	0.018	<0.001	0.03	2.56	<0.02	0.01	0.009	<0.01	<0.01	14.34	0.05	0.002	0.08
634095	Drill Core	2.23	0.001	0.003	1.40	4.04	<2	0.005	<0.001	0.04	2.47	<0.02	0.01	0.011	<0.01	<0.01	21.14	0.05	0.002	0.10
634096	Drill Core	1.56	0.002	0.004	2.39	6.94	<2	0.006	<0.001	0.04	2.99	<0.02	0.01	0.018	<0.01	<0.01	19.01	0.06	0.002	0.09
634097	Drill Core	1.92	0.002	0.003	0.76	3.94	<2	0.008	<0.001	0.02	2.29	<0.02	<0.01	0.010	<0.01	<0.01	7.24	0.07	0.002	0.10
634098	Drill Core	1.21	0.001	0.004	3.50	15.54	3	0.003	<0.001	0.03	0.89	<0.02	0.01	0.050	<0.01	<0.01	17.68	0.03	<0.001	0.05
634099	Drill Core	0.91	0.002	0.004	1.45	6.50	<2	0.006	<0.001	0.02	2.35	<0.02	<0.01	0.017	<0.01	<0.01	7.53	0.06	0.002	0.10
634100	Rock	0.36	<0.001	<0.001	<0.02	0.05	<2	<0.001	<0.001	0.02	0.13	<0.02	0.01	<0.001	<0.01	<0.01	22.19	0.03	<0.001	11.17
634101	Drill Core	1.94	0.002	0.004	1.35	3.29	<2	0.006	<0.001	0.03	1.34	<0.02	0.02	0.008	<0.01	<0.01	18.14	0.09	0.002	0.13
634102	Drill Core	0.94	<0.001	0.001	0.16	<0.01	<2	0.002	<0.001	0.04	0.53	<0.02	0.02	<0.001	<0.01	<0.01	28.47	0.04	<0.001	0.11
634103	Drill Core	2.00	0.002	0.003	0.61	0.24	<2	0.005	<0.001	0.03	0.81	<0.02	0.01	<0.001	<0.01	<0.01	22.06	0.05	0.002	0.12
634104	Drill Core	1.02	0.003	0.006	0.37	0.40	<2	0.010	<0.001	0.02	1.26	<0.02	<0.01	<0.001	<0.01	<0.01	9.13	0.14	0.004	0.20
634105	Drill Core	0.83	0.001	0.002	0.20	0.13	<2	0.004	<0.001	0.04	0.81	<0.02	0.01	<0.001	<0.01	<0.01	20.56	0.03	0.001	0.12
634106	Drill Core	1.71	0.003	0.006	0.19	0.72	<2	0.009	<0.001	0.02	3.75	<0.02	<0.01	0.002	<0.01	<0.01	9.66	0.06	0.003	0.13
634107	Drill Core	2.00	0.001	0.003	0.04	0.47	<2	0.005	<0.001	<0.01	1.03	<0.02	<0.01	<0.001	<0.01	<0.01	3.53	0.05	0.003	0.07
634108	Drill Core	1.85	0.003	0.008	1.00	1.16	<2	0.010	<0.001	0.03	1.65	<0.02	<0.01	0.002	<0.01	<0.01	9.66	0.24	0.003	0.13
634109	Drill Core	0.75	0.002	0.012	3.31	1.28	4	0.008	<0.001	0.05	5.80	<0.02	0.01	0.003	<0.01	<0.01	22.34	0.17	0.003	0.21
634110	Rock Pulp	0.06	<0.001	0.674	5.93	6.67	70	<0.001	0.001	0.09	4.87	<0.02	0.02	0.019	0.02	<0.01	1.27	0.02	0.001	0.25



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: January 10, 2011

Page: 3 of 4 **Part** 2

CERTIFICATE OF ANALYSIS

WHI10000715.1

	Method	7TD	7TD	7TD	7TD	G8SG
	Analyte	Na	K	W	S	SG
	Unit	%	%	%	%	
	MDL	0.01	0.01	0.01	0.05	0
634081	Drill Core	<0.01	1.19	<0.01	1.93	2.10
634082	Drill Core	<0.01	0.89	<0.01	6.62	2.34
634083	Drill Core	<0.01	0.19	<0.01	4.63	2.57
634084	Drill Core	0.01	0.37	<0.01	3.85	2.52
634085	Drill Core	0.01	0.27	<0.01	0.87	2.35
634086	Drill Core	<0.01	0.13	<0.01	1.47	2.50
634087	Drill Core	<0.01	0.42	<0.01	0.86	2.42
634088	Drill Core	<0.01	0.26	<0.01	1.46	2.40
634089	Drill Core	0.01	0.33	<0.01	2.58	2.40
634090	Drill Core	<0.01	0.43	<0.01	1.86	2.28
634091	Drill Core	<0.01	0.42	<0.01	1.95	2.28
634092	Drill Core	<0.01	0.14	<0.01	3.39	2.46
634093	Drill Core	<0.01	0.17	<0.01	0.38	2.36
634094	Drill Core	<0.01	0.28	<0.01	4.71	2.07
634095	Drill Core	<0.01	0.32	<0.01	5.17	2.45
634096	Drill Core	<0.01	0.30	<0.01	7.38	2.55
634097	Drill Core	<0.01	0.44	<0.01	4.64	2.47
634098	Drill Core	<0.01	0.13	<0.01	9.54	2.77
634099	Drill Core	<0.01	0.51	<0.01	6.20	2.56
634100	Rock	0.02	0.03	<0.01	<0.05	2.65
634101	Drill Core	<0.01	0.41	<0.01	3.33	2.46
634102	Drill Core	<0.01	0.14	<0.01	0.60	2.53
634103	Drill Core	<0.01	0.36	<0.01	1.10	2.38
634104	Drill Core	<0.01	0.94	<0.01	1.68	2.28
634105	Drill Core	<0.01	0.25	<0.01	0.97	2.48
634106	Drill Core	<0.01	0.64	<0.01	4.86	2.41
634107	Drill Core	<0.01	0.32	<0.01	1.18	2.39
634108	Drill Core	<0.01	0.55	<0.01	2.56	2.35
634109	Drill Core	<0.01	0.26	<0.01	8.10	2.44
634110	Rock Pulp	2.31	1.35	<0.01	5.65	N.A.



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: January 10, 2011

Page: 4 of 4 Part 1

CERTIFICATE OF ANALYSIS

WHI10000715.1

	Method Analyte Unit MDL	WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD
		Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg	Al
		kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%	%
		0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01	0.01
634111	Drill Core	2.17	0.002	0.005	0.22	0.94	<2	0.005	<0.001	0.02	0.51	<0.02	<0.01	0.002	<0.01	<0.01	11.70	0.21	0.003	0.07	0.35
634112	Drill Core	1.94	0.004	0.011	0.09	0.17	<2	0.007	<0.001	0.04	0.77	<0.02	0.02	<0.001	<0.01	<0.01	21.95	0.38	0.003	0.08	0.37
634113	Drill Core	0.90	0.004	0.006	0.10	0.38	<2	0.007	<0.001	0.03	1.24	<0.02	0.02	<0.001	<0.01	<0.01	22.55	0.06	0.003	0.11	0.59
634114	Drill Core	1.66	0.004	0.008	0.33	1.48	<2	0.009	<0.001	0.02	2.87	<0.02	<0.01	0.003	<0.01	<0.01	10.22	0.43	0.004	0.10	0.72
634115	Drill Core	1.85	0.003	0.006	0.06	0.33	<2	0.006	<0.001	0.02	0.33	<0.02	0.01	<0.001	<0.01	<0.01	14.35	0.24	0.003	0.07	0.42
634116	Drill Core	1.81	0.006	0.020	0.78	1.52	4	0.012	<0.001	0.01	3.72	<0.02	<0.01	0.003	<0.01	<0.01	5.45	0.29	0.005	0.12	0.93
634117	Drill Core	1.27	0.007	0.012	0.30	2.53	4	0.013	<0.001	0.02	0.62	<0.02	<0.01	0.005	<0.01	<0.01	11.18	0.27	0.005	0.13	0.99
634118	Drill Core	2.31	0.008	0.021	0.15	1.16	3	0.017	<0.001	<0.01	2.61	<0.02	<0.01	0.003	<0.01	<0.01	3.05	0.20	0.005	0.15	1.30
634119	Drill Core	1.23	0.008	0.010	0.09	0.87	3	0.021	<0.001	<0.01	0.89	<0.02	<0.01	0.002	<0.01	<0.01	5.02	1.28	0.010	0.19	1.83
634120	Drill Core	0.20	0.001	0.008	0.14	0.04	4	0.015	<0.001	0.01	3.14	<0.02	0.01	<0.001	<0.01	<0.01	11.19	1.92	0.015	0.33	3.27
634121	Drill Core	0.20	0.001	0.008	0.30	0.03	3	0.015	<0.001	0.02	3.60	<0.02	0.01	<0.001	<0.01	<0.01	9.81	1.42	0.013	0.36	3.41
634122	Drill Core	1.15	<0.001	0.002	<0.02	<0.01	<2	0.003	<0.001	0.04	1.60	<0.02	0.02	<0.001	<0.01	<0.01	23.39	0.04	0.002	0.26	1.69
634123	Drill Core	1.41	0.002	0.018	0.62	0.24	4	0.018	<0.001	0.01	4.19	<0.02	0.01	<0.001	<0.01	<0.01	8.39	1.99	0.015	0.19	1.73
634124	Drill Core	2.08	<0.001	0.002	<0.02	<0.01	<2	0.003	<0.001	0.04	1.74	<0.02	0.02	<0.001	<0.01	<0.01	25.33	0.07	0.003	0.33	2.22
634125	Drill Core	1.62	0.001	0.003	0.03	<0.01	<2	0.006	<0.001	0.05	2.29	<0.02	0.02	<0.001	<0.01	<0.01	23.20	0.14	0.004	0.36	2.96
634126	Drill Core	1.26	0.007	0.017	0.06	0.43	4	0.023	<0.001	0.01	4.96	<0.02	0.01	0.002	<0.01	<0.01	8.49	1.57	0.018	0.33	3.26
634127	Drill Core	1.35	0.005	0.009	0.09	0.40	2	0.023	<0.001	<0.01	2.26	<0.02	<0.01	0.002	<0.01	<0.01	3.35	0.27	0.020	0.37	4.38
634128	Drill Core	2.37	0.003	0.008	0.05	0.12	<2	0.018	<0.001	<0.01	2.50	<0.02	<0.01	<0.001	<0.01	<0.01	2.90	0.29	0.011	0.33	4.24



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: January 10, 2011

Page: 4 of 4 **Part** 2

CERTIFICATE OF ANALYSIS

WHI10000715.1

	Method	7TD	7TD	7TD	7TD	G8SG
	Analyte	Na	K	W	S	SG
	Unit	%	%	%	%	
	MDL	0.01	0.01	0.01	0.05	0
634111	Drill Core	<0.01	0.21	<0.01	0.97	2.42
634112	Drill Core	<0.01	0.23	<0.01	0.92	2.27
634113	Drill Core	<0.01	0.34	<0.01	1.58	2.29
634114	Drill Core	<0.01	0.42	<0.01	4.03	2.39
634115	Drill Core	<0.01	0.25	<0.01	0.44	2.34
634116	Drill Core	<0.01	0.55	<0.01	5.01	2.23
634117	Drill Core	<0.01	0.54	<0.01	1.97	2.16
634118	Drill Core	<0.01	0.69	<0.01	3.56	2.06
634119	Drill Core	<0.01	1.01	<0.01	1.37	2.01
634120	Drill Core	<0.01	1.94	<0.01	3.66	2.31
634121	Drill Core	<0.01	2.01	<0.01	4.17	2.29
634122	Drill Core	<0.01	0.87	<0.01	1.81	2.60
634123	Drill Core	<0.01	1.06	<0.01	5.33	2.23
634124	Drill Core	<0.01	1.20	<0.01	2.03	2.51
634125	Drill Core	<0.01	1.74	<0.01	2.66	2.49
634126	Drill Core	0.01	2.06	<0.01	6.34	2.14
634127	Drill Core	0.01	2.92	<0.01	2.75	1.99
634128	Drill Core	0.01	3.00	<0.01	2.80	2.18



Acme Analytical Laboratories (Vancouver) Ltd.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: Selwyn Resources Ltd.

Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: January 10, 2011

Page: 1 of 2 Part 1

QUALITY CONTROL REPORT

WHI10000715.1

	Method Analyte Unit MDL	WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD
		Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg	Al
		kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%	%
		0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01	0.01
Pulp Duplicates																					
634052	Drill Core	1.19	<0.001	0.001	<0.02	<0.01	<2	0.003	<0.001	0.06	0.54	<0.02	0.02	<0.001	<0.01	<0.01	33.60	0.27	<0.001	0.16	0.24
REP 634052	QC		<0.001	0.001	<0.02	<0.01	<2	0.003	<0.001	0.06	0.53	<0.02	0.02	<0.001	<0.01	<0.01	33.75	0.27	<0.001	0.16	0.24
634093	Drill Core	1.37	0.001	0.002	<0.02	<0.01	<2	0.004	<0.001	0.03	0.45	<0.02	0.02	<0.001	<0.01	<0.01	14.90	0.14	0.002	0.07	0.30
REP 634093	QC		0.001	0.002	<0.02	<0.01	<2	0.004	<0.001	0.03	0.46	<0.02	0.02	<0.001	<0.01	<0.01	15.07	0.15	0.002	0.07	0.31
Core Reject Duplicates																					
634053	Drill Core	0.76	<0.001	0.002	<0.02	0.12	<2	0.004	<0.001	0.01	0.61	<0.02	<0.01	<0.001	<0.01	<0.01	5.40	0.76	0.004	0.07	0.58
DUP 634053	QC		<0.001	0.002	<0.02	0.12	<2	0.004	<0.001	<0.01	0.55	<0.02	<0.01	<0.001	<0.01	<0.01	5.57	0.76	0.004	0.07	0.58
634088	Drill Core	1.55	0.001	0.003	<0.02	0.04	<2	0.005	<0.001	0.02	1.34	<0.02	<0.01	<0.001	<0.01	<0.01	8.39	0.04	0.002	0.07	0.47
DUP 634088	QC		0.001	0.003	<0.02	0.02	<2	0.005	<0.001	0.02	1.03	<0.02	<0.01	<0.001	<0.01	<0.01	10.18	0.03	0.002	0.07	0.43
634123	Drill Core	1.41	0.002	0.018	0.62	0.24	4	0.018	<0.001	0.01	4.19	<0.02	0.01	<0.001	<0.01	<0.01	8.39	1.99	0.015	0.19	1.73
DUP 634123	QC		0.001	0.016	0.60	0.21	5	0.018	<0.001	<0.01	3.89	<0.02	0.01	<0.001	<0.01	<0.01	8.55	2.12	0.015	0.19	1.75
Reference Materials																					
STD OREAS131A	Standard		<0.001	0.032	1.65	2.84	31	0.003	0.002	0.17	5.84	<0.02	<0.01	0.008	<0.01	<0.01	5.34	0.05	0.002	3.08	4.53
STD OREAS131A	Standard		<0.001	0.032	1.75	2.94	32	0.003	0.002	0.17	5.80	<0.02	<0.01	0.008	<0.01	<0.01	5.27	0.05	0.002	3.20	4.72
STD OREAS131A	Standard		<0.001	0.032	1.72	2.88	30	0.003	0.002	0.17	5.75	<0.02	<0.01	0.008	<0.01	<0.01	5.20	0.05	0.002	3.19	4.70
STD OREAS131A	Standard		<0.001	0.033	1.73	2.91	31	0.003	0.002	0.18	5.89	<0.02	<0.01	0.008	<0.01	<0.01	5.43	0.06	0.003	3.17	4.72
STD R4T	Standard		0.064	0.508	1.53	3.42	89	0.350	0.041	0.09	24.34	<0.02	0.02	0.019	0.02	<0.01	2.19	0.05	0.019	1.42	3.91
STD R4T	Standard		0.064	0.516	1.59	3.51	89	0.359	0.041	0.09	24.37	<0.02	0.02	0.018	0.01	<0.01	2.23	0.04	0.019	1.44	3.94
STD R4T	Standard		0.064	0.509	1.57	3.48	87	0.353	0.040	0.09	24.06	<0.02	0.02	0.018	0.02	<0.01	2.21	0.05	0.019	1.43	4.00
STD R4T	Standard		0.066	0.511	1.56	3.45	89	0.356	0.042	0.09	24.25	<0.02	0.02	0.019	0.02	<0.01	2.20	0.04	0.017	1.44	4.05
STD SU-1B	Standard		<0.001	1.147	<0.02	0.03	6	1.912	0.066	0.07	25.33	<0.02	0.03	<0.001	<0.01	<0.01	2.23	0.08	0.030	1.78	4.33
STD SU-1B	Standard		<0.001	1.174	<0.02	0.02	7	1.984	0.066	0.07	25.41	<0.02	0.03	<0.001	<0.01	<0.01	2.29	0.06	0.032	1.82	4.45
STD SU-1B	Standard		<0.001	1.205	<0.02	0.03	6	2.001	0.067	0.07	25.44	<0.02	0.03	<0.001	<0.01	<0.01	2.27	0.06	0.032	1.82	4.48
STD SU-1B	Standard		<0.001	1.207	<0.02	0.03	6	1.993	0.068	0.07	25.27	<0.02	0.03	<0.001	<0.01	<0.01	2.25	0.06	0.030	1.81	4.48
STD R4T Expected			0.062	0.502	1.518	3.376	86	0.339	0.039	0.086	24.07	0.0087	0.0185	0.018	0.0138	0.0018	2.166	0.045	0.018	1.384	3.897
STD OREAS131A Expected			0.001	0.0322	1.72	2.83	30.9	0.0027	0.0023	0.1722	5.8166	0.0082	0.0028	0.0081	0.0047	0.001	5.286	0.0536	0.0025	3.1182	4.6057
STD SU-1B Expected			0.0004	1.185	0.0058	0.0235	6.4	1.97	0.0672	0.0703	25.54	0.00025	0.03	0.0003	0.00002	0.0003	2.21	0.06	0.032	1.79	4.39
BLK	Blank		<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	<0.01	<0.01	<0.02	<0.01	<0.001	<0.01	<0.01	<0.01	<0.01	<0.001	<0.01	<0.01



Acme Analytical Laboratories (Vancouver) Ltd.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: Selwyn Resources Ltd.

Suite 700 - 509 Richards Street

Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: January 10, 2011

Page: 1 of 2 **Part** 2

QUALITY CONTROL REPORT

WHI10000715.1

Method		7TD	7TD	7TD	7TD	G8SG
Analyte		Na	K	W	S	SG
Unit		%	%	%	%	%
MDL		0.01	0.01	0.01	0.05	0
Pulp Duplicates						
634052	Drill Core	0.01	0.13	<0.01	0.62	2.45
REP 634052	QC	0.01	0.13	<0.01	0.62	
634093	Drill Core	<0.01	0.17	<0.01	0.38	2.36
REP 634093	QC	<0.01	0.18	<0.01	0.38	
Core Reject Duplicates						
634053	Drill Core	<0.01	0.33	<0.01	0.49	2.36
DUP 634053	QC	<0.01	0.33	<0.01	0.48	2.40
634088	Drill Core	<0.01	0.26	<0.01	1.46	2.40
DUP 634088	QC	<0.01	0.24	<0.01	1.13	2.43
634123	Drill Core	<0.01	1.06	<0.01	5.33	2.23
DUP 634123	QC	<0.01	1.08	<0.01	4.94	2.22
Reference Materials						
STD OREAS131A	Standard	0.15	3.41	<0.01	4.67	
STD OREAS131A	Standard	0.15	3.45	<0.01	4.96	
STD OREAS131A	Standard	0.15	3.42	<0.01	4.73	
STD OREAS131A	Standard	0.16	3.44	<0.01	4.95	
STD R4T	Standard	0.94	1.19	<0.01	11.57	
STD R4T	Standard	0.92	1.17	<0.01	12.59	
STD R4T	Standard	0.93	1.16	<0.01	12.24	
STD R4T	Standard	0.94	1.20	<0.01	14.39	
STD SU-1B	Standard	1.70	0.62	<0.01	8.12	
STD SU-1B	Standard	1.72	0.61	<0.01	8.71	
STD SU-1B	Standard	1.69	0.61	<0.01	8.75	
STD SU-1B	Standard	1.74	0.63	<0.01	10.25	
STD R4T Expected		0.9	1.153	0.00016	12.9903	
STD OREAS131A Expected		0.1501	3.1584	0.0005	4.8	
STD SU-1B Expected		1.662	0.6	0.0007	8.76	
BLK	Blank	<0.01	<0.01	<0.01	<0.05	



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: January 10, 2011

Page: 2 of 2 **Part** 1

QUALITY CONTROL REPORT

WHI10000715.1

		WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD
		Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg
		kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%
		0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01
BLK	Blank		<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	<0.01	<0.01	<0.02	<0.01	<0.001	<0.01	<0.01	<0.01	<0.01	<0.001	<0.01
BLK	Blank		<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	<0.01	<0.01	<0.02	<0.01	<0.001	<0.01	<0.01	<0.01	<0.01	<0.001	<0.01
BLK	Blank		<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	<0.01	<0.01	<0.02	<0.01	<0.001	<0.01	<0.01	<0.01	<0.01	<0.001	<0.01
Prep Wash																				
G1	Prep Blank		<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	0.08	2.44	<0.02	0.07	<0.001	<0.01	<0.01	2.38	0.08	0.001	0.62
G1	Prep Blank		<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	0.08	2.43	<0.02	0.07	<0.001	<0.01	<0.01	2.41	0.09	0.001	0.62



Acme Analytical Laboratories (Vancouver) Ltd.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: **Selwyn Resources Ltd.**

Suite 700 - 509 Richards Street

Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: January 10, 2011

Page: 2 of 2 **Part** 2

QUALITY CONTROL REPORT

WHI10000715.1

		7TD Na %	7TD K %	7TD W %	7TD S %	G8SG SG
		0.01	0.01	0.01	0.05	0
BLK	Blank	<0.01	<0.01	<0.01	<0.05	
BLK	Blank	<0.01	<0.01	<0.01	<0.05	
BLK	Blank	<0.01	<0.01	<0.01	<0.05	
Prep Wash						
G1	Prep Blank	2.72	3.10	<0.01	<0.05	2.76
G1	Prep Blank	2.76	3.15	<0.01	<0.05	2.70



1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: Selwyn Resources Ltd.

Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Submitted By: Jason K. Dunning

Receiving Lab: Canada-Whitehorse

Received: December 22, 2010

Report Date: January 24, 2011

Page: 1 of 4

CERTIFICATE OF ANALYSIS

WHI10000714.2

CLIENT JOB INFORMATION

Project: Selwyn Project
Shipment ID:
P.O. Number 1175
Number of Samples: 61

SAMPLE DISPOSAL

STOR-PLP Store After 90 days Invoice for Storage
STOR-RJT Store After 90 days Invoice for Storage

Acme does not accept responsibility for samples left at the laboratory after 90 days without prior written instructions for sample storage or return.

Invoice To: Selwyn Chihong Mining Ltd.
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6
Canada

CC:

SAMPLE PREPARATION AND ANALYTICAL PROCEDURES

Method Code	Number of Samples	Code Description	Test Wgt (g)	Report Status	Lab
R200-250	59	Crush split and pulverize 250g drill core to 200 mesh			WHI
7TD2	61	4 Acid digestion ICP-ES analysis.	0.5	Completed	VAN
G812	61	Specific Gravity on Pulp		Completed	VAN

ADDITIONAL COMMENTS

Version 2: Re-analysis of 7TD2 for Sample IDs 633878, 633879, 633881, 633881 DUP, 633882 & 633883 from core rejects including 633880 Rock Pulp



This report supersedes all previous preliminary and final reports with this file number dated prior to the date on this certificate. Signature indicates final approval; preliminary reports are unsigned and should be used for reference only.
All results are considered the confidential property of the client. Acme assumes the liabilities for actual cost of analysis only.
** asterisk indicates that an analytical result could not be provided due to unusually high levels of interference from other elements.



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: January 24, 2011

Page: 2 of 4 Part 1

CERTIFICATE OF ANALYSIS

WHI10000714.2

	Method Analyte Unit MDL	WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD
		Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg	Al
		kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%	%
		0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01	0.01
633851	Drill Core	1.98	0.001	0.004	0.13	0.16	3	0.012	<0.001	<0.01	1.32	<0.02	0.01	<0.001	<0.01	<0.01	8.06	2.50	0.009	0.73	3.54
633852	Drill Core	1.99	<0.001	0.010	0.78	5.99	7	0.005	<0.001	0.02	4.54	<0.02	0.02	0.016	<0.01	<0.01	11.72	0.20	0.003	0.28	0.93
633853	Drill Core	0.76	<0.001	0.004	0.07	0.04	<2	0.011	<0.001	<0.01	1.48	<0.02	0.01	<0.001	<0.01	<0.01	7.75	2.07	0.011	0.73	3.57
633854	Drill Core	1.21	<0.001	0.003	0.02	0.20	3	0.006	<0.001	<0.01	0.77	<0.02	<0.01	<0.001	<0.01	<0.01	2.08	0.81	0.004	0.12	1.15
633855	Drill Core	0.94	0.001	0.003	<0.02	0.11	2	0.005	<0.001	0.02	0.79	<0.02	<0.01	<0.001	<0.01	<0.01	6.18	0.55	0.004	0.11	1.13
633856	Drill Core	1.27	0.002	0.003	0.03	0.68	3	0.009	<0.001	<0.01	0.93	<0.02	<0.01	0.003	<0.01	<0.01	3.17	0.68	0.004	0.14	1.56
633857	Drill Core	1.42	0.006	0.009	1.61	7.76	3	0.011	<0.001	0.01	5.13	<0.02	<0.01	0.031	<0.01	<0.01	0.79	0.06	0.004	0.15	1.73
633858	Drill Core	1.73	<0.001	0.005	3.61	18.86	4	0.002	<0.001	0.01	1.30	<0.02	<0.01	0.085	<0.01	<0.01	0.60	0.02	0.002	0.04	0.34
633859	Drill Core	1.29	<0.001	0.005	3.17	16.03	3	0.004	<0.001	0.01	2.76	<0.02	<0.01	0.085	<0.01	<0.01	0.72	0.10	0.002	0.06	0.68
633860	Drill Core	0.65	0.001	0.006	7.04	10.88	5	0.003	<0.001	0.01	3.97	<0.02	<0.01	0.050	<0.01	<0.01	3.17	0.03	0.002	0.05	0.44
633861	Drill Core	0.72	0.002	0.007	5.55	13.23	5	0.005	<0.001	0.02	4.72	<0.02	<0.01	0.062	<0.01	<0.01	3.12	0.04	0.002	0.06	0.66
633862	Drill Core	1.11	0.003	0.003	0.47	2.23	3	0.006	<0.001	0.06	3.35	<0.02	0.01	0.007	<0.01	<0.01	17.21	0.04	0.002	0.11	0.62
633863	Drill Core	1.64	0.003	0.006	1.11	6.83	3	0.008	<0.001	0.02	4.90	<0.02	<0.01	0.016	<0.01	<0.01	2.96	0.05	0.002	0.09	0.95
633864	Drill Core	0.59	0.001	0.002	2.45	3.76	4	0.004	<0.001	0.06	1.80	<0.02	0.01	0.009	<0.01	<0.01	19.60	0.07	0.002	0.12	0.54
633865	Drill Core	1.58	<0.001	<0.001	0.02	0.20	<2	<0.001	<0.001	0.07	0.35	<0.02	0.01	<0.001	<0.01	<0.01	28.93	0.01	<0.001	0.12	0.09
633866	Drill Core	1.22	0.001	0.001	0.08	0.86	<2	0.004	<0.001	<0.01	0.61	<0.02	<0.01	0.002	<0.01	<0.01	3.87	0.04	0.002	0.05	0.45
633867	Drill Core	1.76	0.003	0.003	0.39	3.17	<2	0.009	<0.001	<0.01	1.40	<0.02	<0.01	0.009	<0.01	<0.01	2.82	0.04	0.003	0.09	1.02
633868	Drill Core	1.39	0.005	0.003	0.06	0.51	2	0.009	<0.001	0.02	1.35	<0.02	<0.01	0.001	<0.01	<0.01	8.58	0.03	0.002	0.11	1.28
633869	Drill Core	0.60	0.005	0.021	1.80	14.71	3	0.010	<0.001	0.04	9.49	<0.02	<0.01	0.041	<0.01	<0.01	2.87	0.06	0.002	0.08	1.03
633870	Rock	0.39	<0.001	<0.001	<0.02	0.02	<2	<0.001	<0.001	0.03	0.24	<0.02	<0.01	<0.001	<0.01	<0.01	19.90	0.02	<0.001	10.96	0.20
633871	Drill Core	1.65	<0.001	0.001	0.27	0.33	<2	<0.001	<0.001	0.06	6.55	<0.02	0.02	<0.001	<0.01	<0.01	28.93	0.02	<0.001	0.09	0.07
633872	Drill Core	2.50	<0.001	<0.001	0.18	0.63	<2	0.002	<0.001	0.04	0.68	<0.02	0.02	0.002	<0.01	<0.01	28.25	0.07	<0.001	0.11	0.45
633873	Drill Core	1.01	0.001	0.003	0.80	3.82	3	0.006	<0.001	0.04	2.36	<0.02	0.01	0.011	<0.01	<0.01	19.46	0.09	0.002	0.14	1.07
633874	Drill Core	1.05	0.001	0.002	1.17	5.90	<2	0.004	<0.001	0.02	2.21	<0.02	<0.01	0.016	<0.01	<0.01	4.78	0.07	0.002	0.09	0.72
633875	Drill Core	1.26	0.002	0.003	1.39	5.37	2	0.006	<0.001	0.03	2.61	<0.02	<0.01	0.014	<0.01	<0.01	11.57	0.07	0.002	0.13	0.97
633876	Drill Core	0.86	<0.001	<0.001	0.56	1.40	<2	0.002	<0.001	0.04	1.47	<0.02	0.01	0.004	<0.01	<0.01	24.80	0.05	<0.001	0.09	0.38
633877	Drill Core	1.34	0.001	0.002	0.75	4.20	<2	0.002	<0.001	0.04	2.03	<0.02	0.02	0.012	<0.01	<0.01	26.38	0.03	<0.001	0.08	0.32
633878	Drill Core	1.91	0.002	0.003	1.41	5.15	<2	0.005	<0.001	0.02	2.77	<0.02	<0.01	0.013	<0.01	<0.01	8.42	0.06	<0.001	0.09	0.64
633879	Drill Core	0.55	0.002	0.009	3.75	28.18	5	0.004	<0.001	0.03	2.89	<0.02	<0.01	0.057	<0.01	<0.01	8.81	0.04	<0.001	0.06	0.38
633880	Rock Pulp	0.06	<0.001	0.486	1.41	2.96	20	<0.001	<0.001	0.43	2.62	<0.02	0.02	0.016	<0.01	<0.01	4.88	0.02	<0.001	0.33	4.38



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**

Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: January 24, 2011

Page: 2 of 4 Part 2

CERTIFICATE OF ANALYSIS

WHI10000714.2

	Method	7TD	7TD	7TD	7TD	G8SG
	Analyte	Na	K	W	S	SG
	Unit	%	%	%	%	
	MDL	0.01	0.01	0.01	0.05	0
633851	Drill Core	0.02	2.26	<0.01	1.46	2.06
633852	Drill Core	<0.01	0.67	<0.01	9.10	2.50
633853	Drill Core	0.02	2.40	<0.01	1.57	2.38
633854	Drill Core	<0.01	0.70	<0.01	0.85	2.32
633855	Drill Core	<0.01	0.74	<0.01	0.78	2.30
633856	Drill Core	<0.01	0.97	<0.01	1.33	2.25
633857	Drill Core	<0.01	1.02	<0.01	10.57	2.37
633858	Drill Core	<0.01	0.20	<0.01	11.28	2.81
633859	Drill Core	<0.01	0.42	<0.01	11.71	2.67
633860	Drill Core	<0.01	0.24	<0.01	11.37	2.76
633861	Drill Core	<0.01	0.36	<0.01	13.12	2.79
633862	Drill Core	<0.01	0.33	<0.01	5.48	2.57
633863	Drill Core	<0.01	0.58	<0.01	9.44	2.54
633864	Drill Core	<0.01	0.29	<0.01	4.32	2.54
633865	Drill Core	<0.01	0.04	<0.01	0.51	2.50
633866	Drill Core	<0.01	0.26	<0.01	0.95	2.39
633867	Drill Core	<0.01	0.60	<0.01	3.01	2.30
633868	Drill Core	<0.01	0.83	<0.01	1.73	2.26
633869	Drill Core	<0.01	0.69	<0.01	18.25	2.88
633870	Rock	<0.01	0.04	<0.01	0.11	2.64
633871	Drill Core	<0.01	0.04	<0.01	8.30	2.76
633872	Drill Core	<0.01	0.22	<0.01	1.12	2.40
633873	Drill Core	<0.01	0.60	<0.01	4.90	2.50
633874	Drill Core	<0.01	0.46	<0.01	5.76	2.50
633875	Drill Core	<0.01	0.59	<0.01	6.02	2.46
633876	Drill Core	<0.01	0.20	<0.01	2.46	2.52
633877	Drill Core	<0.01	0.17	<0.01	4.76	2.50
633878	Drill Core	0.03	0.36	<0.01	6.23	2.52
633879	Drill Core	<0.01	0.24	<0.01	17.99	2.78
633880	Rock Pulp	1.72	1.25	<0.01	3.30	N.A.



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: January 24, 2011

Page: 3 of 4 Part 1

CERTIFICATE OF ANALYSIS

WHI10000714.2

	Method Analyte Unit MDL	WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD
		Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg
		kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%
		0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01
633881	Drill Core	0.80	0.002	0.002	3.44	2.33	<2	0.005	<0.001	0.03	1.43	<0.02	0.01	0.007	<0.01	<0.01	19.60	0.05	0.001	0.11
633882	Drill Core	0.97	0.002	0.002	1.82	7.31	<2	0.003	<0.001	0.03	1.17	<0.02	0.01	0.023	<0.01	<0.01	18.87	0.04	<0.001	0.07
633883	Drill Core	1.75	<0.001	0.001	0.10	0.50	<2	0.003	<0.001	0.03	0.41	<0.02	0.01	0.002	<0.01	<0.01	21.63	0.04	<0.001	0.09
633884	Drill Core	1.59	0.002	0.002	0.21	0.16	<2	0.005	<0.001	0.03	1.03	<0.02	0.01	<0.001	<0.01	<0.01	16.86	0.07	0.002	0.13
633885	Drill Core	0.56	<0.001	0.004	3.55	5.77	<2	0.002	<0.001	0.05	1.04	<0.02	0.01	0.027	<0.01	<0.01	22.04	0.04	<0.001	0.08
633886	Drill Core	1.96	0.002	0.003	0.33	0.55	<2	0.006	<0.001	0.02	1.21	<0.02	0.01	0.002	<0.01	<0.01	15.69	0.07	0.002	0.14
633887	Drill Core	1.10	<0.001	0.003	0.17	0.15	<2	0.003	<0.001	0.04	2.70	<0.02	0.02	<0.001	<0.01	<0.01	25.51	0.03	<0.001	0.10
633888	Drill Core	1.42	0.003	0.007	0.55	0.51	<2	0.008	<0.001	0.03	0.92	<0.02	<0.01	0.001	<0.01	<0.01	14.36	0.07	0.002	0.15
633889	Drill Core	1.01	<0.001	0.002	0.06	0.10	<2	0.003	<0.001	0.03	0.41	<0.02	0.01	<0.001	<0.01	<0.01	19.88	0.03	<0.001	0.06
633890	Drill Core	0.75	0.001	0.002	0.62	1.00	<2	0.005	<0.001	0.02	0.92	<0.02	<0.01	0.002	<0.01	<0.01	4.88	0.03	0.002	0.08
633891	Drill Core	0.73	0.001	0.002	0.14	0.86	<2	0.005	<0.001	0.02	0.83	<0.02	<0.01	0.002	<0.01	<0.01	7.00	0.04	0.002	0.08
633892	Drill Core	1.50	0.003	0.007	1.15	1.85	3	0.010	<0.001	0.03	1.71	<0.02	<0.01	0.003	<0.01	<0.01	11.68	0.26	0.004	0.14
633893	Drill Core	1.40	0.002	0.003	0.33	1.65	<2	0.008	<0.001	<0.01	0.91	<0.02	<0.01	0.003	<0.01	<0.01	2.30	0.26	0.003	0.07
633894	Drill Core	1.14	0.005	0.012	0.34	1.63	<2	0.010	<0.001	0.02	1.26	<0.02	<0.01	0.004	<0.01	<0.01	10.61	0.41	0.003	0.10
633895	Drill Core	1.84	0.001	0.001	0.25	0.30	<2	0.003	<0.001	0.04	0.34	<0.02	0.02	<0.001	<0.01	<0.01	32.04	0.21	<0.001	0.16
633896	Drill Core	1.55	0.002	0.003	2.27	0.57	3	0.005	<0.001	0.04	0.37	<0.02	0.02	0.001	<0.01	<0.01	23.69	0.12	0.001	0.07
633897	Drill Core	0.92	0.002	0.004	0.09	0.18	<2	0.005	<0.001	0.02	0.33	<0.02	0.01	<0.001	<0.01	<0.01	16.29	0.21	0.002	0.06
633898	Drill Core	0.71	0.007	0.014	2.10	2.50	9	0.014	<0.001	0.01	0.90	<0.02	<0.01	0.005	<0.01	<0.01	7.24	0.37	0.007	0.15
633899	Drill Core	0.72	0.004	0.012	0.14	0.78	<2	0.009	<0.001	0.02	0.47	<0.02	0.01	0.002	<0.01	<0.01	14.27	0.26	0.003	0.10
633900	Rock	0.43	<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	0.02	0.29	<0.02	0.01	<0.001	<0.01	<0.01	20.83	0.03	<0.001	10.99
633901	Drill Core	0.72	0.008	0.020	0.43	1.33	3	0.016	<0.001	0.01	4.60	<0.02	<0.01	0.003	<0.01	<0.01	8.11	0.30	0.006	0.18
633902	Drill Core	0.80	0.007	0.010	0.07	0.59	<2	0.016	<0.001	<0.01	0.76	<0.02	<0.01	0.002	<0.01	<0.01	2.66	0.26	0.005	0.16
633903	Drill Core	0.72	0.010	0.016	0.06	0.04	<2	0.014	<0.001	0.01	0.63	<0.02	<0.01	<0.001	<0.01	<0.01	6.11	0.06	0.006	0.15
633904	Drill Core	1.34	0.004	0.013	0.32	0.85	4	0.021	<0.001	<0.01	1.68	<0.02	<0.01	0.002	<0.01	<0.01	7.58	2.42	0.016	0.22
633905	Drill Core	1.20	<0.001	0.002	0.03	<0.01	<2	0.005	<0.001	0.03	1.98	<0.02	0.02	<0.001	<0.01	<0.01	20.33	0.05	0.003	0.34
633906	Drill Core	1.11	0.003	0.006	<0.02	0.03	2	0.019	<0.001	<0.01	2.33	<0.02	<0.01	<0.001	<0.01	<0.01	3.91	0.18	0.013	0.39
633907	Drill Core	1.33	0.002	0.010	0.55	0.69	4	0.018	<0.001	0.01	3.04	<0.02	0.01	0.002	<0.01	<0.01	11.43	2.56	0.015	0.18
633908	Drill Core	2.57	<0.001	0.002	<0.02	<0.01	<2	0.003	<0.001	0.04	1.95	<0.02	0.02	<0.001	<0.01	<0.01	24.58	0.03	0.003	0.31
633909	Drill Core	1.88	0.008	0.010	0.04	0.38	3	0.023	<0.001	0.01	3.33	<0.02	0.01	0.002	<0.01	<0.01	7.54	1.89	0.017	0.38
633910	Rock Pulp	0.06	<0.001	0.678	6.30	6.86	71	0.001	0.001	0.09	4.87	<0.02	0.02	0.019	0.04	<0.01	1.42	0.02	<0.001	0.25



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: January 24, 2011

Page: 3 of 4 **Part** 2

CERTIFICATE OF ANALYSIS

WHI10000714.2

	Method	7TD	7TD	7TD	7TD	G8SG
	Analyte	Na	K	W	S	SG
	Unit	%	%	%	%	
	MDL	0.01	0.01	0.01	0.05	0
633881	Drill Core	<0.01	0.33	<0.01	3.32	2.54
633882	Drill Core	<0.01	0.25	<0.01	5.25	2.61
633883	Drill Core	<0.01	0.24	<0.01	0.71	2.34
633884	Drill Core	<0.01	0.52	<0.01	1.28	2.39
633885	Drill Core	<0.01	0.12	<0.01	4.88	2.68
633886	Drill Core	<0.01	0.59	<0.01	1.74	2.31
633887	Drill Core	<0.01	0.24	<0.01	3.46	2.46
633888	Drill Core	<0.01	0.70	<0.01	1.35	2.27
633889	Drill Core	<0.01	0.14	<0.01	0.54	2.55
633890	Drill Core	<0.01	0.29	<0.01	1.45	2.45
633891	Drill Core	<0.01	0.27	<0.01	1.33	2.45
633892	Drill Core	<0.01	0.60	<0.01	3.07	2.30
633893	Drill Core	<0.01	0.30	<0.01	1.79	2.35
633894	Drill Core	<0.01	0.40	<0.01	2.28	2.25
633895	Drill Core	<0.01	0.09	<0.01	0.58	2.36
633896	Drill Core	<0.01	0.16	<0.01	1.02	2.40
633897	Drill Core	<0.01	0.17	<0.01	0.45	2.39
633898	Drill Core	<0.01	0.73	<0.01	2.44	2.20
633899	Drill Core	<0.01	0.35	<0.01	0.88	2.24
633900	Rock	<0.01	0.04	<0.01	0.10	2.62
633901	Drill Core	<0.01	0.65	<0.01	6.34	2.18
633902	Drill Core	<0.01	0.63	<0.01	1.07	2.08
633903	Drill Core	<0.01	0.70	<0.01	0.60	2.14
633904	Drill Core	<0.01	1.13	<0.01	2.32	1.94
633905	Drill Core	<0.01	1.56	<0.01	2.33	2.48
633906	Drill Core	0.01	3.35	<0.01	2.51	2.03
633907	Drill Core	<0.01	1.16	<0.01	3.93	2.29
633908	Drill Core	<0.01	1.33	<0.01	2.25	2.54
633909	Drill Core	0.01	2.34	<0.01	3.88	2.00
633910	Rock Pulp	2.31	1.32	<0.01	5.70	N.A.



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: January 24, 2011

Page: 4 of 4 **Part** 1

CERTIFICATE OF ANALYSIS

WHI10000714.2

	Method Analyte Unit MDL	WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD
		Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg	Al
		kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%	%
		0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01	0.01
633911	Drill Core	1.88	0.005	0.009	0.02	0.05	<2	0.024	<0.001	<0.01	2.44	<0.02	<0.01	<0.001	<0.01	<0.01	2.37	0.48	0.014	0.39	4.18



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: January 24, 2011

Page: 4 of 4 **Part** 2

CERTIFICATE OF ANALYSIS

WHI10000714.2

Method		7TD	7TD	7TD	7TD	G8SG
Analyte		Na	K	W	S	SG
Unit		%	%	%	%	
MDL		0.01	0.01	0.01	0.05	0
633911	Drill Core	<0.01	3.02	<0.01	2.70	1.93



Acme Analytical Laboratories (Vancouver) Ltd.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: Selwyn Resources Ltd.

Suite 700 - 509 Richards Street

Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: January 24, 2011

Page: 1 of 1 Part 1

QUALITY CONTROL REPORT

WHI10000714.2

	Method Analyte Unit MDL	WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD
		Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg	Al
		kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%	%
		0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01	0.01
Pulp Duplicates																					
633865	Drill Core	1.58	<0.001	<0.001	0.02	0.20	<2	<0.001	<0.001	0.07	0.35	<0.02	0.01	<0.001	<0.01	<0.01	28.93	0.01	<0.001	0.12	0.09
REP 633865	QC		<0.001	<0.001	0.02	0.21	<2	<0.001	<0.001	0.07	0.36	<0.02	0.01	<0.001	<0.01	<0.01	29.84	0.01	<0.001	0.12	0.09
633880	Rock Pulp	0.06	<0.001	0.486	1.41	2.96	20	<0.001	<0.001	0.43	2.62	<0.02	0.02	0.016	<0.01	<0.01	4.88	0.02	<0.001	0.33	4.38
REP 633880	QC		<0.001	0.474	1.41	2.92	18	<0.001	<0.001	0.42	2.62	<0.02	0.02	0.017	<0.01	<0.01	4.88	0.02	<0.001	0.32	4.33
633910	Rock Pulp	0.06	<0.001	0.678	6.30	6.86	71	0.001	0.001	0.09	4.87	<0.02	0.02	0.019	0.04	<0.01	1.42	0.02	<0.001	0.25	5.20
REP 633910	QC		<0.001	0.676	6.27	6.83	71	<0.001	0.001	0.10	4.88	<0.02	0.02	0.018	0.04	<0.01	1.42	0.02	<0.001	0.25	5.31
Core Reject Duplicates																					
633881	Drill Core	0.80	0.002	0.002	3.44	2.33	<2	0.005	<0.001	0.03	1.43	<0.02	0.01	0.007	<0.01	<0.01	19.60	0.05	0.001	0.11	0.60
DUP 633881	QC		0.002	0.002	3.48	2.27	<2	0.005	<0.001	0.03	1.46	<0.02	0.01	0.007	<0.01	<0.01	19.72	0.05	0.002	0.11	0.59
Reference Materials																					
STD OREAS131A	Standard		<0.001	0.032	1.75	2.94	32	0.003	0.002	0.17	5.80	<0.02	<0.01	0.008	<0.01	<0.01	5.27	0.05	0.002	3.20	4.72
STD OREAS131A	Standard		<0.001	0.031	1.67	2.84	31	0.002	0.002	0.17	5.65	<0.02	<0.01	0.008	<0.01	<0.01	5.24	0.05	0.003	3.10	4.58
STD OREAS131A	Standard		<0.001	0.033	1.73	2.91	31	0.003	0.002	0.17	5.95	<0.02	<0.01	0.009	<0.01	<0.01	5.43	0.06	0.002	3.21	4.75
STD R4T	Standard		0.064	0.516	1.59	3.51	89	0.359	0.041	0.09	24.37	<0.02	0.02	0.018	0.01	<0.01	2.23	0.04	0.019	1.44	3.94
STD R4T	Standard		0.063	0.507	1.54	3.43	87	0.350	0.040	0.09	24.00	<0.02	0.02	0.018	0.02	<0.01	2.19	0.05	0.018	1.42	3.98
STD R4T	Standard		0.070	0.527	1.61	3.50	97	0.366	0.045	0.09	24.67	<0.02	0.02	0.019	0.02	<0.01	2.24	0.05	0.018	1.44	4.06
STD SU-1B	Standard		<0.001	1.174	<0.02	0.02	7	1.984	0.066	0.07	25.41	<0.02	0.03	<0.001	<0.01	<0.01	2.29	0.06	0.032	1.82	4.45
STD SU-1B	Standard		<0.001	1.127	<0.02	0.02	7	1.914	0.064	0.07	24.63	<0.02	0.03	<0.001	<0.01	<0.01	2.18	0.06	0.027	1.77	4.33
STD SU-1B	Standard		<0.001	1.214	<0.02	0.03	6	2.026	0.068	0.07	25.76	<0.02	0.03	0.002	<0.01	<0.01	2.27	0.06	0.030	1.82	4.47
STD R4T Expected			0.062	0.502	1.518	3.376	86	0.339	0.039	0.086	24.07	0.0087	0.0185	0.018	0.0138	0.0018	2.166	0.045	0.018	1.384	3.897
STD OREAS131A Expected			0.001	0.0322	1.72	2.83	30.9	0.0027	0.0023	0.1722	5.8166	0.0082	0.0028	0.0081	0.0047	0.001	5.286	0.0536	0.0025	3.1182	4.6057
STD SU-1B Expected			0.0004	1.185	0.0058	0.0235	6.4	1.97	0.0672	0.0703	25.54	0.00025	0.03	0.0003	0.00002	0.0003	2.21	0.06	0.032	1.79	4.39
BLK	Blank		<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	<0.01	<0.01	<0.02	<0.01	<0.001	<0.01	<0.01	<0.01	<0.01	<0.001	<0.01	<0.01
BLK	Blank		<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	<0.01	<0.01	<0.02	<0.01	<0.001	<0.01	<0.01	<0.01	<0.01	<0.001	<0.01	<0.01
BLK	Blank		<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	<0.01	<0.01	<0.02	<0.01	<0.001	<0.01	<0.01	<0.01	<0.01	<0.001	<0.01	<0.01
Prep Wash																					
G1	Prep Blank		<0.001	<0.001	<0.02	0.01	2	<0.001	<0.001	0.07	2.20	<0.02	0.07	<0.001	<0.01	<0.01	2.26	0.08	<0.001	0.58	7.18
G1	Prep Blank		<0.001	<0.001	<0.02	0.01	<2	<0.001	<0.001	0.07	2.24	<0.02	0.07	<0.001	<0.01	<0.01	2.32	0.08	<0.001	0.60	7.67



Acme Analytical Laboratories (Vancouver) Ltd.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: Selwyn Resources Ltd.

Suite 700 - 509 Richards Street

Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: January 24, 2011

Page: 1 of 1 Part 2

QUALITY CONTROL REPORT

WHI10000714.2

Method		7TD	7TD	7TD	7TD	G8SG
Analyte		Na	K	W	S	SG
Unit		%	%	%	%	%
MDL		0.01	0.01	0.01	0.05	0
Pulp Duplicates						
633865	Drill Core	<0.01	0.04	<0.01	0.51	2.50
REP 633865	QC	<0.01	0.05	<0.01	0.51	
633880	Rock Pulp	1.72	1.25	<0.01	3.30	N.A.
REP 633880	QC	1.71	1.24	<0.01	3.27	
633910	Rock Pulp	2.31	1.32	<0.01	5.70	N.A.
REP 633910	QC	2.27	1.34	<0.01	5.71	
Core Reject Duplicates						
633881	Drill Core	<0.01	0.33	<0.01	3.32	2.54
DUP 633881	QC	<0.01	0.33	<0.01	3.39	2.54
Reference Materials						
STD OREAS131A	Standard	0.15	3.45	<0.01	4.96	
STD OREAS131A	Standard	0.15	3.26	<0.01	4.60	
STD OREAS131A	Standard	0.15	3.44	<0.01	4.90	
STD R4T	Standard	0.92	1.17	<0.01	12.59	
STD R4T	Standard	0.92	1.15	<0.01	12.41	
STD R4T	Standard	0.93	1.21	<0.01	12.99	
STD SU-1B	Standard	1.72	0.61	<0.01	8.71	
STD SU-1B	Standard	1.64	0.59	<0.01	8.43	
STD SU-1B	Standard	1.70	0.62	<0.01	9.69	
STD R4T Expected		0.9	1.153	0.00016	12.9903	
STD OREAS131A Expected		0.1501	3.1584	0.0005	4.8	
STD SU-1B Expected		1.662	0.6	0.0007	8.76	
BLK	Blank	<0.01	<0.01	<0.01	<0.05	
BLK	Blank	<0.01	<0.01	<0.01	<0.05	
BLK	Blank	<0.01	<0.01	<0.01	<0.05	
Prep Wash						
G1	Prep Blank	2.70	2.25	<0.01	0.05	2.67
G1	Prep Blank	2.73	2.52	<0.01	<0.05	2.71



1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**

Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Submitted By: Jason K. Dunning

Receiving Lab: Canada-Whitehorse

Received: December 22, 2010

Report Date: January 17, 2011

Page: 1 of 4

CERTIFICATE OF ANALYSIS

WHI10000714.1

CLIENT JOB INFORMATION

Project: Selwyn Project
Shipment ID:
P.O. Number 1175
Number of Samples: 61

SAMPLE DISPOSAL

STOR-PLP Store After 90 days Invoice for Storage
STOR-RJT Store After 90 days Invoice for Storage

Acme does not accept responsibility for samples left at the laboratory after 90 days without prior written instructions for sample storage or return.

Invoice To: Selwyn Resources Ltd.
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6
Canada

CC:

SAMPLE PREPARATION AND ANALYTICAL PROCEDURES

Method Code	Number of Samples	Code Description	Test Wgt (g)	Report Status	Lab
R200-250	59	Crush split and pulverize 250g drill core to 200 mesh			WHI
7TD2	61	4 Acid digestion ICP-ES analysis.	0.5	Completed	VAN
G812	61	Specific Gravity on Pulp		Completed	VAN

ADDITIONAL COMMENTS

DUP not match - Subject to recheck on Sample IDs 633878, 633879, 633881, 633881 DUP, 633882 & 633883 from core rejects



This report supersedes all previous preliminary and final reports with this file number dated prior to the date on this certificate. Signature indicates final approval; preliminary reports are unsigned and should be used for reference only.
All results are considered the confidential property of the client. Acme assumes the liabilities for actual cost of analysis only.
** asterisk indicates that an analytical result could not be provided due to unusually high levels of interference from other elements.



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: January 17, 2011

Page: 2 of 4 Part 1

CERTIFICATE OF ANALYSIS

WHI10000714.1

	Method Analyte Unit MDL	WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD
		Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg	Al
		kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%	%
		0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01	0.01
633851	Drill Core	1.98	0.001	0.004	0.13	0.16	3	0.012	<0.001	<0.01	1.32	<0.02	0.01	<0.001	<0.01	<0.01	8.06	2.50	0.009	0.73	3.54
633852	Drill Core	1.99	<0.001	0.010	0.78	5.99	7	0.005	<0.001	0.02	4.54	<0.02	0.02	0.016	<0.01	<0.01	11.72	0.20	0.003	0.28	0.93
633853	Drill Core	0.76	<0.001	0.004	0.07	0.04	<2	0.011	<0.001	<0.01	1.48	<0.02	0.01	<0.001	<0.01	<0.01	7.75	2.07	0.011	0.73	3.57
633854	Drill Core	1.21	<0.001	0.003	0.02	0.20	3	0.006	<0.001	<0.01	0.77	<0.02	<0.01	<0.001	<0.01	<0.01	2.08	0.81	0.004	0.12	1.15
633855	Drill Core	0.94	0.001	0.003	<0.02	0.11	2	0.005	<0.001	0.02	0.79	<0.02	<0.01	<0.001	<0.01	<0.01	6.18	0.55	0.004	0.11	1.13
633856	Drill Core	1.27	0.002	0.003	0.03	0.68	3	0.009	<0.001	<0.01	0.93	<0.02	<0.01	0.003	<0.01	<0.01	3.17	0.68	0.004	0.14	1.56
633857	Drill Core	1.42	0.006	0.009	1.61	7.76	3	0.011	<0.001	0.01	5.13	<0.02	<0.01	0.031	<0.01	<0.01	0.79	0.06	0.004	0.15	1.73
633858	Drill Core	1.73	<0.001	0.005	3.61	18.86	4	0.002	<0.001	0.01	1.30	<0.02	<0.01	0.085	<0.01	<0.01	0.60	0.02	0.002	0.04	0.34
633859	Drill Core	1.29	<0.001	0.005	3.17	16.03	3	0.004	<0.001	0.01	2.76	<0.02	<0.01	0.085	<0.01	<0.01	0.72	0.10	0.002	0.06	0.68
633860	Drill Core	0.65	0.001	0.006	7.04	10.88	5	0.003	<0.001	0.01	3.97	<0.02	<0.01	0.050	<0.01	<0.01	3.17	0.03	0.002	0.05	0.44
633861	Drill Core	0.72	0.002	0.007	5.55	13.23	5	0.005	<0.001	0.02	4.72	<0.02	<0.01	0.062	<0.01	<0.01	3.12	0.04	0.002	0.06	0.66
633862	Drill Core	1.11	0.003	0.003	0.47	2.23	3	0.006	<0.001	0.06	3.35	<0.02	0.01	0.007	<0.01	<0.01	17.21	0.04	0.002	0.11	0.62
633863	Drill Core	1.64	0.003	0.006	1.11	6.83	3	0.008	<0.001	0.02	4.90	<0.02	<0.01	0.016	<0.01	<0.01	2.96	0.05	0.002	0.09	0.95
633864	Drill Core	0.59	0.001	0.002	2.45	3.76	4	0.004	<0.001	0.06	1.80	<0.02	0.01	0.009	<0.01	<0.01	19.60	0.07	0.002	0.12	0.54
633865	Drill Core	1.58	<0.001	<0.001	0.02	0.20	<2	<0.001	<0.001	0.07	0.35	<0.02	0.01	<0.001	<0.01	<0.01	28.93	0.01	<0.001	0.12	0.09
633866	Drill Core	1.22	0.001	0.001	0.08	0.86	<2	0.004	<0.001	<0.01	0.61	<0.02	<0.01	0.002	<0.01	<0.01	3.87	0.04	0.002	0.05	0.45
633867	Drill Core	1.76	0.003	0.003	0.39	3.17	<2	0.009	<0.001	<0.01	1.40	<0.02	<0.01	0.009	<0.01	<0.01	2.82	0.04	0.003	0.09	1.02
633868	Drill Core	1.39	0.005	0.003	0.06	0.51	2	0.009	<0.001	0.02	1.35	<0.02	<0.01	0.001	<0.01	<0.01	8.58	0.03	0.002	0.11	1.28
633869	Drill Core	0.60	0.005	0.021	1.80	14.71	3	0.010	<0.001	0.04	9.49	<0.02	<0.01	0.041	<0.01	<0.01	2.87	0.06	0.002	0.08	1.03
633870	Rock	0.39	<0.001	<0.001	<0.02	0.02	<2	<0.001	<0.001	0.03	0.24	<0.02	<0.01	<0.001	<0.01	<0.01	19.90	0.02	<0.001	10.96	0.20
633871	Drill Core	1.65	<0.001	0.001	0.27	0.33	<2	<0.001	<0.001	0.06	6.55	<0.02	0.02	<0.001	<0.01	<0.01	28.93	0.02	<0.001	0.09	0.07
633872	Drill Core	2.50	<0.001	<0.001	0.18	0.63	<2	0.002	<0.001	0.04	0.68	<0.02	0.02	0.002	<0.01	<0.01	28.25	0.07	<0.001	0.11	0.45
633873	Drill Core	1.01	0.001	0.003	0.80	3.82	3	0.006	<0.001	0.04	2.36	<0.02	0.01	0.011	<0.01	<0.01	19.46	0.09	0.002	0.14	1.07
633874	Drill Core	1.05	0.001	0.002	1.17	5.90	<2	0.004	<0.001	0.02	2.21	<0.02	<0.01	0.016	<0.01	<0.01	4.78	0.07	0.002	0.09	0.72
633875	Drill Core	1.26	0.002	0.003	1.39	5.37	2	0.006	<0.001	0.03	2.61	<0.02	<0.01	0.014	<0.01	<0.01	11.57	0.07	0.002	0.13	0.97
633876	Drill Core	0.86	<0.001	<0.001	0.56	1.40	<2	0.002	<0.001	0.04	1.47	<0.02	0.01	0.004	<0.01	<0.01	24.80	0.05	<0.001	0.09	0.38
633877	Drill Core	1.34	0.001	0.002	0.75	4.20	<2	0.002	<0.001	0.04	2.03	<0.02	0.02	0.012	<0.01	<0.01	26.38	0.03	<0.001	0.08	0.32
633878	Drill Core	1.91	0.002	0.003	1.41	5.32	3	0.006	<0.001	0.03	3.04	<0.02	<0.01	0.015	<0.01	<0.01	8.95	0.06	<0.001	0.10	0.66
633879	Drill Core	0.55	0.003	0.009	2.86	21.14	6	0.008	<0.001	0.04	4.74	<0.02	<0.01	0.043	<0.01	<0.01	12.28	0.07	0.001	0.09	0.66
633880	Rock Pulp	0.06	<0.001	0.476	1.39	3.00	18	<0.001	<0.001	0.47	2.67	<0.02	0.02	0.018	<0.01	<0.01	4.87	0.01	0.001	0.32	4.13



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**

Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: January 17, 2011

Page: 2 of 4 Part 2

CERTIFICATE OF ANALYSIS

WHI10000714.1

	Method	7TD	7TD	7TD	7TD	G8SG
Analyte	Na	K	W	S	SG	
Unit	%	%	%	%		
MDL	0.01	0.01	0.01	0.05	0	
633851	Drill Core	0.02	2.26	<0.01	1.46	2.06
633852	Drill Core	<0.01	0.67	<0.01	9.10	2.50
633853	Drill Core	0.02	2.40	<0.01	1.57	2.38
633854	Drill Core	<0.01	0.70	<0.01	0.85	2.32
633855	Drill Core	<0.01	0.74	<0.01	0.78	2.30
633856	Drill Core	<0.01	0.97	<0.01	1.33	2.25
633857	Drill Core	<0.01	1.02	<0.01	10.57	2.37
633858	Drill Core	<0.01	0.20	<0.01	11.28	2.81
633859	Drill Core	<0.01	0.42	<0.01	11.71	2.67
633860	Drill Core	<0.01	0.24	<0.01	11.37	2.76
633861	Drill Core	<0.01	0.36	<0.01	13.12	2.79
633862	Drill Core	<0.01	0.33	<0.01	5.48	2.57
633863	Drill Core	<0.01	0.58	<0.01	9.44	2.54
633864	Drill Core	<0.01	0.29	<0.01	4.32	2.54
633865	Drill Core	<0.01	0.04	<0.01	0.51	2.50
633866	Drill Core	<0.01	0.26	<0.01	0.95	2.39
633867	Drill Core	<0.01	0.60	<0.01	3.01	2.30
633868	Drill Core	<0.01	0.83	<0.01	1.73	2.26
633869	Drill Core	<0.01	0.69	<0.01	18.25	2.88
633870	Rock	<0.01	0.04	<0.01	0.11	2.64
633871	Drill Core	<0.01	0.04	<0.01	8.30	2.76
633872	Drill Core	<0.01	0.22	<0.01	1.12	2.40
633873	Drill Core	<0.01	0.60	<0.01	4.90	2.50
633874	Drill Core	<0.01	0.46	<0.01	5.76	2.50
633875	Drill Core	<0.01	0.59	<0.01	6.02	2.46
633876	Drill Core	<0.01	0.20	<0.01	2.46	2.52
633877	Drill Core	<0.01	0.17	<0.01	4.76	2.50
633878	Drill Core	<0.01	0.39	<0.01	6.14	2.52
633879	Drill Core	<0.01	0.44	<0.01	15.72	2.78
633880	Rock Pulp	1.72	1.24	<0.01	3.03	N.A.



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: January 17, 2011

Page: 3 of 4 Part 1

CERTIFICATE OF ANALYSIS

WHI10000714.1

	Method Analyte Unit MDL	WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD
		Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg
		kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%
		0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01
633881	Drill Core	0.80	0.002	0.002	3.22	1.49	<2	0.005	<0.001	0.03	1.49	<0.02	0.01	0.004	<0.01	<0.01	19.20	0.05	0.002	0.11
633882	Drill Core	0.97	0.002	0.003	1.99	9.39	<2	0.004	<0.001	0.03	1.70	<0.02	0.01	0.029	<0.01	<0.01	16.18	0.05	<0.001	0.08
633883	Drill Core	1.75	<0.001	0.001	0.09	0.52	<2	0.003	<0.001	0.03	0.40	<0.02	0.01	0.002	<0.01	<0.01	21.29	0.04	<0.001	0.09
633884	Drill Core	1.59	0.002	0.002	0.21	0.16	<2	0.005	<0.001	0.03	1.03	<0.02	0.01	<0.001	<0.01	<0.01	16.86	0.07	0.002	0.13
633885	Drill Core	0.56	<0.001	0.004	3.55	5.77	<2	0.002	<0.001	0.05	1.04	<0.02	0.01	0.027	<0.01	<0.01	22.04	0.04	<0.001	0.08
633886	Drill Core	1.96	0.002	0.003	0.33	0.55	<2	0.006	<0.001	0.02	1.21	<0.02	0.01	0.002	<0.01	<0.01	15.69	0.07	0.002	0.14
633887	Drill Core	1.10	<0.001	0.003	0.17	0.15	<2	0.003	<0.001	0.04	2.70	<0.02	0.02	<0.001	<0.01	<0.01	25.51	0.03	<0.001	0.10
633888	Drill Core	1.42	0.003	0.007	0.55	0.51	<2	0.008	<0.001	0.03	0.92	<0.02	<0.01	0.001	<0.01	<0.01	14.36	0.07	0.002	0.15
633889	Drill Core	1.01	<0.001	0.002	0.06	0.10	<2	0.003	<0.001	0.03	0.41	<0.02	0.01	<0.001	<0.01	<0.01	19.88	0.03	<0.001	0.06
633890	Drill Core	0.75	0.001	0.002	0.62	1.00	<2	0.005	<0.001	0.02	0.92	<0.02	<0.01	0.002	<0.01	<0.01	4.88	0.03	0.002	0.08
633891	Drill Core	0.73	0.001	0.002	0.14	0.86	<2	0.005	<0.001	0.02	0.83	<0.02	<0.01	0.002	<0.01	<0.01	7.00	0.04	0.002	0.08
633892	Drill Core	1.50	0.003	0.007	1.15	1.85	3	0.010	<0.001	0.03	1.71	<0.02	<0.01	0.003	<0.01	<0.01	11.68	0.26	0.004	0.14
633893	Drill Core	1.40	0.002	0.003	0.33	1.65	<2	0.008	<0.001	<0.01	0.91	<0.02	<0.01	0.003	<0.01	<0.01	2.30	0.26	0.003	0.07
633894	Drill Core	1.14	0.005	0.012	0.34	1.63	<2	0.010	<0.001	0.02	1.26	<0.02	<0.01	0.004	<0.01	<0.01	10.61	0.41	0.003	0.10
633895	Drill Core	1.84	0.001	0.001	0.25	0.30	<2	0.003	<0.001	0.04	0.34	<0.02	0.02	<0.001	<0.01	<0.01	32.04	0.21	<0.001	0.16
633896	Drill Core	1.55	0.002	0.003	2.27	0.57	3	0.005	<0.001	0.04	0.37	<0.02	0.02	0.001	<0.01	<0.01	23.69	0.12	0.001	0.07
633897	Drill Core	0.92	0.002	0.004	0.09	0.18	<2	0.005	<0.001	0.02	0.33	<0.02	0.01	<0.001	<0.01	<0.01	16.29	0.21	0.002	0.06
633898	Drill Core	0.71	0.007	0.014	2.10	2.50	9	0.014	<0.001	0.01	0.90	<0.02	<0.01	0.005	<0.01	<0.01	7.24	0.37	0.007	0.15
633899	Drill Core	0.72	0.004	0.012	0.14	0.78	<2	0.009	<0.001	0.02	0.47	<0.02	0.01	0.002	<0.01	<0.01	14.27	0.26	0.003	0.10
633900	Rock	0.43	<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	0.02	0.29	<0.02	0.01	<0.001	<0.01	<0.01	20.83	0.03	<0.001	10.99
633901	Drill Core	0.72	0.008	0.020	0.43	1.33	3	0.016	<0.001	0.01	4.60	<0.02	<0.01	0.003	<0.01	<0.01	8.11	0.30	0.006	0.18
633902	Drill Core	0.80	0.007	0.010	0.07	0.59	<2	0.016	<0.001	<0.01	0.76	<0.02	<0.01	0.002	<0.01	<0.01	2.66	0.26	0.005	0.16
633903	Drill Core	0.72	0.010	0.016	0.06	0.04	<2	0.014	<0.001	0.01	0.63	<0.02	<0.01	<0.001	<0.01	<0.01	6.11	0.06	0.006	0.15
633904	Drill Core	1.34	0.004	0.013	0.32	0.85	4	0.021	<0.001	<0.01	1.68	<0.02	<0.01	0.002	<0.01	<0.01	7.58	2.42	0.016	0.22
633905	Drill Core	1.20	<0.001	0.002	0.03	<0.01	<2	0.005	<0.001	0.03	1.98	<0.02	0.02	<0.001	<0.01	<0.01	20.33	0.05	0.003	0.34
633906	Drill Core	1.11	0.003	0.006	<0.02	0.03	2	0.019	<0.001	<0.01	2.33	<0.02	<0.01	<0.001	<0.01	<0.01	3.91	0.18	0.013	0.39
633907	Drill Core	1.33	0.002	0.010	0.55	0.69	4	0.018	<0.001	0.01	3.04	<0.02	0.01	0.002	<0.01	<0.01	11.43	2.56	0.015	0.18
633908	Drill Core	2.57	<0.001	0.002	<0.02	<0.01	<2	0.003	<0.001	0.04	1.95	<0.02	0.02	<0.001	<0.01	<0.01	24.58	0.03	0.003	0.31
633909	Drill Core	1.88	0.008	0.010	0.04	0.38	3	0.023	<0.001	0.01	3.33	<0.02	0.01	0.002	<0.01	<0.01	7.54	1.89	0.017	0.38
633910	Rock Pulp	0.06	<0.001	0.678	6.30	6.86	71	0.001	0.001	0.09	4.87	<0.02	0.02	0.019	0.04	<0.01	1.42	0.02	<0.001	0.25



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**

Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: January 17, 2011

Page: 3 of 4 Part 2

CERTIFICATE OF ANALYSIS

WHI10000714.1

	Method	7TD	7TD	7TD	7TD	G8SG
	Analyte	Na	K	W	S	SG
	Unit	%	%	%	%	
	MDL	0.01	0.01	0.01	0.05	0
633881	Drill Core	<0.01	0.33	<0.01	2.69	2.54
633882	Drill Core	<0.01	0.36	<0.01	6.63	2.61
633883	Drill Core	<0.01	0.24	<0.01	0.78	2.34
633884	Drill Core	<0.01	0.52	<0.01	1.28	2.39
633885	Drill Core	<0.01	0.12	<0.01	4.88	2.68
633886	Drill Core	<0.01	0.59	<0.01	1.74	2.31
633887	Drill Core	<0.01	0.24	<0.01	3.46	2.46
633888	Drill Core	<0.01	0.70	<0.01	1.35	2.27
633889	Drill Core	<0.01	0.14	<0.01	0.54	2.55
633890	Drill Core	<0.01	0.29	<0.01	1.45	2.45
633891	Drill Core	<0.01	0.27	<0.01	1.33	2.45
633892	Drill Core	<0.01	0.60	<0.01	3.07	2.30
633893	Drill Core	<0.01	0.30	<0.01	1.79	2.35
633894	Drill Core	<0.01	0.40	<0.01	2.28	2.25
633895	Drill Core	<0.01	0.09	<0.01	0.58	2.36
633896	Drill Core	<0.01	0.16	<0.01	1.02	2.40
633897	Drill Core	<0.01	0.17	<0.01	0.45	2.39
633898	Drill Core	<0.01	0.73	<0.01	2.44	2.20
633899	Drill Core	<0.01	0.35	<0.01	0.88	2.24
633900	Rock	<0.01	0.04	<0.01	0.10	2.62
633901	Drill Core	<0.01	0.65	<0.01	6.34	2.18
633902	Drill Core	<0.01	0.63	<0.01	1.07	2.08
633903	Drill Core	<0.01	0.70	<0.01	0.60	2.14
633904	Drill Core	<0.01	1.13	<0.01	2.32	1.94
633905	Drill Core	<0.01	1.56	<0.01	2.33	2.48
633906	Drill Core	0.01	3.35	<0.01	2.51	2.03
633907	Drill Core	<0.01	1.16	<0.01	3.93	2.29
633908	Drill Core	<0.01	1.33	<0.01	2.25	2.54
633909	Drill Core	0.01	2.34	<0.01	3.88	2.00
633910	Rock Pulp	2.31	1.32	<0.01	5.70	N.A.



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: January 17, 2011

Page: 4 of 4 **Part** 1

CERTIFICATE OF ANALYSIS

WHI10000714.1

	Method Analyte Unit MDL	WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD
		Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg	Al
		kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%	%
		0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01	0.01
633911	Drill Core	1.88	0.005	0.009	0.02	0.05	<2	0.024	<0.001	<0.01	2.44	<0.02	<0.01	<0.001	<0.01	<0.01	2.37	0.48	0.014	0.39	4.18



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**

Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: January 17, 2011

Page: 4 of 4 Part 2

CERTIFICATE OF ANALYSIS

WHI10000714.1

Method		7TD	7TD	7TD	7TD	G8SG
Analyte		Na	K	W	S	SG
Unit		%	%	%	%	
MDL		0.01	0.01	0.01	0.05	0
633911	Drill Core	<0.01	3.02	<0.01	2.70	1.93



Acme Analytical Laboratories (Vancouver) Ltd.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: **Selwyn Resources Ltd.**

Suite 700 - 509 Richards Street

Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: January 17, 2011

Page: 1 of 1 Part 1

QUALITY CONTROL REPORT

WHI10000714.1

	Method Analyte Unit MDL	WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD
		Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg	Al
		kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%	%
		0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01	0.01
Pulp Duplicates																					
633865	Drill Core	1.58	<0.001	<0.001	0.02	0.20	<2	<0.001	<0.001	0.07	0.35	<0.02	0.01	<0.001	<0.01	<0.01	28.93	0.01	<0.001	0.12	0.09
REP 633865	QC		<0.001	<0.001	0.02	0.21	<2	<0.001	<0.001	0.07	0.36	<0.02	0.01	<0.001	<0.01	<0.01	29.84	0.01	<0.001	0.12	0.09
633880	Rock Pulp	0.06	<0.001	0.476	1.39	3.00	18	<0.001	<0.001	0.47	2.67	<0.02	0.02	0.018	<0.01	<0.01	4.87	0.01	0.001	0.32	4.13
REP 633880	QC		<0.001	0.456	1.34	2.80	23	<0.001	<0.001	0.43	2.54	<0.02	0.02	0.018	<0.01	<0.01	4.64	0.02	0.001	0.31	4.05
633910	Rock Pulp	0.06	<0.001	0.678	6.30	6.86	71	0.001	0.001	0.09	4.87	<0.02	0.02	0.019	0.04	<0.01	1.42	0.02	<0.001	0.25	5.20
REP 633910	QC		<0.001	0.676	6.27	6.83	71	<0.001	0.001	0.10	4.88	<0.02	0.02	0.018	0.04	<0.01	1.42	0.02	<0.001	0.25	5.31
Core Reject Duplicates																					
633881	Drill Core	0.80	0.002	0.002	3.22	1.49	<2	0.005	<0.001	0.03	1.49	<0.02	0.01	0.004	<0.01	<0.01	19.20	0.05	0.002	0.11	0.62
DUP 633881	QC		0.002	0.002	2.94	3.23	<2	0.005	<0.001	0.03	1.34	<0.02	0.01	0.010	<0.01	<0.01	17.72	0.05	0.002	0.11	0.66
Reference Materials																					
STD OREAS131A	Standard		<0.001	0.032	1.75	2.94	32	0.003	0.002	0.17	5.80	<0.02	<0.01	0.008	<0.01	<0.01	5.27	0.05	0.002	3.20	4.72
STD OREAS131A	Standard		<0.001	0.031	1.67	2.84	31	0.002	0.002	0.17	5.65	<0.02	<0.01	0.008	<0.01	<0.01	5.24	0.05	0.003	3.10	4.58
STD OREAS131A	Standard		<0.001	0.033	1.72	2.89	32	0.003	0.002	0.18	5.90	<0.02	<0.01	0.008	<0.01	<0.01	5.28	0.06	0.002	3.14	4.66
STD R4T	Standard		0.064	0.516	1.59	3.51	89	0.359	0.041	0.09	24.37	<0.02	0.02	0.018	0.01	<0.01	2.23	0.04	0.019	1.44	3.94
STD R4T	Standard		0.063	0.507	1.54	3.43	87	0.350	0.040	0.09	24.00	<0.02	0.02	0.018	0.02	<0.01	2.19	0.05	0.018	1.42	3.98
STD R4T	Standard		0.063	0.514	1.57	3.47	89	0.353	0.041	0.09	24.38	<0.02	0.02	0.018	0.02	<0.01	2.21	0.04	0.019	1.44	4.04
STD SU-1B	Standard		<0.001	1.174	<0.02	0.02	7	1.984	0.066	0.07	25.41	<0.02	0.03	<0.001	<0.01	<0.01	2.29	0.06	0.032	1.82	4.45
STD SU-1B	Standard		<0.001	1.127	<0.02	0.02	7	1.914	0.064	0.07	24.63	<0.02	0.03	<0.001	<0.01	<0.01	2.18	0.06	0.027	1.77	4.33
STD SU-1B	Standard		<0.001	1.187	<0.02	0.03	7	1.969	0.067	0.07	25.46	<0.02	0.03	<0.001	0.02	<0.01	2.23	0.06	0.032	1.81	4.45
STD R4T Expected			0.062	0.502	1.518	3.376	86	0.339	0.039	0.086	24.07	0.0087	0.0185	0.018	0.0138	0.0018	2.166	0.045	0.018	1.384	3.897
STD OREAS131A Expected			0.001	0.0322	1.72	2.83	30.9	0.0027	0.0023	0.1722	5.8166	0.0082	0.0028	0.0081	0.0047	0.001	5.286	0.0536	0.0025	3.1182	4.6057
STD SU-1B Expected			0.0004	1.185	0.0058	0.0235	6.4	1.97	0.0672	0.0703	25.54	0.00025	0.03	0.0003	0.00002	0.0003	2.21	0.06	0.032	1.79	4.39
BLK	Blank		<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	<0.01	<0.01	<0.02	<0.01	<0.001	<0.01	<0.01	<0.01	<0.01	<0.001	<0.01	<0.01
BLK	Blank		<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	<0.01	<0.01	<0.02	<0.01	<0.001	<0.01	<0.01	<0.01	<0.01	<0.001	<0.01	<0.01
BLK	Blank		<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	<0.01	<0.01	<0.02	<0.01	<0.001	<0.01	<0.01	<0.01	<0.01	<0.001	<0.01	<0.01
Prep Wash																					
G1	Prep Blank		<0.001	<0.001	<0.02	0.01	2	<0.001	<0.001	0.07	2.20	<0.02	0.07	<0.001	<0.01	<0.01	2.26	0.08	<0.001	0.58	7.18
G1	Prep Blank		<0.001	<0.001	<0.02	0.01	<2	<0.001	<0.001	0.07	2.24	<0.02	0.07	<0.001	<0.01	<0.01	2.32	0.08	<0.001	0.60	7.67



Acme Analytical Laboratories (Vancouver) Ltd.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: Selwyn Resources Ltd.

Suite 700 - 509 Richards Street

Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: January 17, 2011

Page: 1 of 1 Part 2

QUALITY CONTROL REPORT

WHI10000714.1

Method		7TD	7TD	7TD	7TD	G8SG
Analyte		Na	K	W	S	SG
Unit		%	%	%	%	%
MDL		0.01	0.01	0.01	0.05	0
Pulp Duplicates						
633865	Drill Core	<0.01	0.04	<0.01	0.51	2.50
REP 633865	QC	<0.01	0.05	<0.01	0.51	
633880	Rock Pulp	1.72	1.24	<0.01	3.03	N.A.
REP 633880	QC	1.62	1.17	<0.01	2.86	
633910	Rock Pulp	2.31	1.32	<0.01	5.70	N.A.
REP 633910	QC	2.27	1.34	<0.01	5.71	
Core Reject Duplicates						
633881	Drill Core	<0.01	0.33	<0.01	2.69	2.54
DUP 633881	QC	<0.01	0.36	<0.01	3.34	2.54
Reference Materials						
STD OREAS131A	Standard	0.15	3.45	<0.01	4.96	
STD OREAS131A	Standard	0.15	3.26	<0.01	4.60	
STD OREAS131A	Standard	0.15	3.39	<0.01	4.53	
STD R4T	Standard	0.92	1.17	<0.01	12.59	
STD R4T	Standard	0.92	1.15	<0.01	12.41	
STD R4T	Standard	0.94	1.20	<0.01	11.72	
STD SU-1B	Standard	1.72	0.61	<0.01	8.71	
STD SU-1B	Standard	1.64	0.59	<0.01	8.43	
STD SU-1B	Standard	1.73	0.62	<0.01	8.14	
STD R4T Expected		0.9	1.153	0.00016	12.9903	
STD OREAS131A Expected		0.1501	3.1584	0.0005	4.8	
STD SU-1B Expected		1.662	0.6	0.0007	8.76	
BLK	Blank	<0.01	<0.01	<0.01	<0.05	
BLK	Blank	<0.01	<0.01	<0.01	<0.05	
BLK	Blank	<0.01	<0.01	<0.01	<0.05	
Prep Wash						
G1	Prep Blank	2.70	2.25	<0.01	0.05	2.67
G1	Prep Blank	2.73	2.52	<0.01	<0.05	2.71



1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**

Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Submitted By: Jason K. Dunning

Receiving Lab: Canada-Whitehorse

Received: December 22, 2010

Report Date: January 14, 2011

Page: 1 of 3

CERTIFICATE OF ANALYSIS

WHI10000713.1

CLIENT JOB INFORMATION

Project: Selwyn Project
Shipment ID:
P.O. Number 1175
Number of Samples: 44

SAMPLE DISPOSAL

STOR-PLP Store After 90 days Invoice for Storage
STOR-RJT Store After 90 days Invoice for Storage

Acme does not accept responsibility for samples left at the laboratory after 90 days without prior written instructions for sample storage or return.

Invoice To: Selwyn Resources Ltd.
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6
Canada

CC:

SAMPLE PREPARATION AND ANALYTICAL PROCEDURES

Method Code	Number of Samples	Code Description	Test Wgt (g)	Report Status	Lab
R200-250	44	Crush split and pulverize 250g drill core to 200 mesh			WHI
7TD2	44	4 Acid digestion ICP-ES analysis.	0.5	Completed	VAN
G812	44	Specific Gravity on Pulp		Completed	VAN

ADDITIONAL COMMENTS



This report supersedes all previous preliminary and final reports with this file number dated prior to the date on this certificate. Signature indicates final approval; preliminary reports are unsigned and should be used for reference only.
All results are considered the confidential property of the client. Acme assumes the liabilities for actual cost of analysis only.
** asterisk indicates that an analytical result could not be provided due to unusually high levels of interference from other elements.



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: January 14, 2011

Page: 2 of 3 Part 1

CERTIFICATE OF ANALYSIS

WHI10000713.1

	Method Analyte Unit MDL	WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD
		Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg	Al
		kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%	%
		0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01	0.01
631651	Drill Core	1.18	0.006	0.006	<0.02	0.54	3	0.019	0.001	<0.01	2.09	<0.02	<0.01	0.005	<0.01	<0.01	1.13	0.09	0.010	0.30	3.81
631652	Drill Core	0.86	0.007	0.005	<0.02	1.11	4	0.019	0.001	<0.01	2.21	<0.02	<0.01	0.009	<0.01	<0.01	0.98	0.08	0.010	0.29	3.72
631653	Drill Core	1.42	0.005	0.006	<0.02	0.38	<2	0.015	0.001	<0.01	1.86	<0.02	<0.01	0.004	<0.01	<0.01	2.17	0.06	0.009	0.29	3.52
631654	Drill Core	0.37	0.007	0.004	<0.02	0.44	<2	0.017	0.001	<0.01	1.89	<0.02	<0.01	0.004	<0.01	<0.01	1.52	0.08	0.008	0.38	4.09
631655	Drill Core	1.91	<0.001	0.007	<0.02	0.02	<2	0.010	<0.001	0.01	1.28	<0.02	<0.01	<0.001	<0.01	<0.01	7.92	1.60	0.005	0.21	2.24
631656	Drill Core	1.37	0.005	0.009	0.16	6.20	4	0.009	<0.001	0.03	7.50	<0.02	<0.01	0.015	<0.01	<0.01	10.92	0.06	0.002	0.10	0.94
631657	Drill Core	2.43	0.005	0.008	0.37	7.55	4	0.010	<0.001	0.02	4.52	<0.02	<0.01	0.018	<0.01	<0.01	5.15	0.08	0.002	0.10	1.05
631658	Drill Core	1.86	0.001	0.001	0.03	0.24	<2	0.003	<0.001	0.03	0.63	<0.02	0.01	<0.001	<0.01	<0.01	21.56	0.02	<0.001	0.05	0.23
631659	Drill Core	0.60	0.001	0.002	0.03	0.63	<2	0.004	<0.001	0.02	0.67	<0.02	<0.01	0.002	<0.01	<0.01	8.63	0.08	0.001	0.05	0.42
631660	Drill Core	0.49	0.002	0.012	2.47	11.35	4	0.006	<0.001	0.03	10.22	<0.02	<0.01	0.040	<0.01	<0.01	6.71	0.04	0.002	0.04	0.33
631661	Drill Core	0.45	0.001	0.011	2.53	12.97	3	0.005	<0.001	0.03	8.81	<0.02	<0.01	0.047	<0.01	<0.01	6.66	0.04	0.001	0.04	0.33
631662	Drill Core	0.50	<0.001	0.002	0.88	1.32	3	0.003	<0.001	0.02	2.60	<0.02	<0.01	0.005	<0.01	<0.01	14.60	0.04	0.001	0.05	0.30
631663	Drill Core	0.28	<0.001	0.003	0.05	1.27	<2	0.005	<0.001	0.02	2.81	<0.02	<0.01	0.003	<0.01	<0.01	6.16	0.05	0.002	0.06	0.40
631664	Drill Core	1.98	<0.001	0.002	<0.02	0.16	2	0.003	<0.001	0.02	1.15	<0.02	<0.01	<0.001	<0.01	<0.01	13.95	0.33	0.003	0.10	0.65
631665	Drill Core	1.77	<0.001	0.004	<0.02	<0.01	3	0.008	<0.001	<0.01	1.12	<0.02	<0.01	<0.001	<0.01	<0.01	4.91	1.24	0.006	0.11	1.07
631666	Drill Core	2.15	<0.001	0.003	<0.02	<0.01	<2	0.007	<0.001	<0.01	1.16	<0.02	<0.01	<0.001	<0.01	<0.01	3.09	1.12	0.006	0.09	0.93
631667	Drill Core	1.89	<0.001	0.005	<0.02	<0.01	<2	0.009	<0.001	<0.01	1.11	<0.02	<0.01	<0.001	<0.01	<0.01	5.74	1.43	0.007	0.12	1.32
631668	Drill Core	0.74	<0.001	0.007	<0.02	0.05	<2	0.013	<0.001	<0.01	0.94	<0.02	<0.01	<0.001	<0.01	<0.01	6.00	2.11	0.007	0.12	1.31
631669	Drill Core	0.26	0.001	0.002	0.66	0.78	<2	0.004	<0.001	0.02	0.98	<0.02	<0.01	0.003	<0.01	<0.01	6.92	0.25	0.003	0.10	0.95
631670	Rock	0.45	<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	0.02	0.13	<0.02	<0.01	<0.001	<0.01	<0.01	20.77	0.03	<0.001	11.18	0.09
631671	Drill Core	1.87	0.005	0.009	0.04	0.09	2	0.009	<0.001	0.01	1.32	<0.02	<0.01	0.001	<0.01	<0.01	5.37	0.16	0.004	0.12	0.85
631672	Drill Core	1.64	0.004	0.013	1.39	7.22	6	0.008	<0.001	0.02	6.61	<0.02	<0.01	0.027	<0.01	<0.01	2.70	0.05	0.002	0.10	0.91
631673	Drill Core	0.29	<0.001	0.010	5.30	15.78	4	0.003	<0.001	<0.01	3.14	<0.02	<0.01	0.071	<0.01	<0.01	0.08	<0.01	0.002	0.03	0.40
631674	Drill Core	1.44	<0.001	0.008	3.44	13.99	4	0.002	<0.001	0.01	5.53	<0.02	<0.01	0.066	<0.01	<0.01	1.60	0.01	0.002	0.02	0.25
631675	Drill Core	2.11	0.003	0.004	1.95	1.64	3	0.007	<0.001	0.01	1.53	<0.02	<0.01	0.009	<0.01	<0.01	2.81	0.03	0.004	0.10	1.03
631676	Drill Core	1.19	0.003	0.007	1.27	4.09	3	0.007	<0.001	0.01	3.52	<0.02	<0.01	0.023	<0.01	<0.01	0.37	0.02	0.002	0.09	0.88
631677	Drill Core	1.79	0.005	0.009	0.62	2.09	<2	0.012	<0.001	0.02	11.89	<0.02	<0.01	0.007	<0.01	<0.01	3.44	0.08	0.004	0.14	1.09
631678	Drill Core	1.16	0.006	0.013	0.21	14.26	6	0.010	0.001	0.03	7.17	<0.02	<0.01	0.034	0.01	<0.01	3.53	0.08	0.003	0.12	1.19
631679	Drill Core	0.86	<0.001	0.006	0.17	1.83	<2	0.004	<0.001	0.06	1.91	<0.02	<0.01	0.005	<0.01	<0.01	17.71	0.03	<0.001	0.10	0.36
631680	Rock Pulp	0.06	<0.001	0.667	6.16	7.02	70	<0.001	<0.001	0.09	4.95	<0.02	0.02	0.018	0.03	<0.01	1.36	0.02	0.002	0.26	5.19



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: January 14, 2011

Page: 2 of 3 **Part** 2

CERTIFICATE OF ANALYSIS

WHI10000713.1

	Method	7TD	7TD	7TD	7TD	G8SG
	Analyte	Na	K	W	S	SG
	Unit	%	%	%	%	
	MDL	0.01	0.01	0.01	0.05	0
631651	Drill Core	<0.01	2.67	<0.01	2.34	2.23
631652	Drill Core	<0.01	2.29	<0.01	2.76	2.27
631653	Drill Core	<0.01	2.08	<0.01	2.06	2.19
631654	Drill Core	<0.01	2.68	<0.01	1.96	2.26
631655	Drill Core	<0.01	0.95	<0.01	1.21	2.34
631656	Drill Core	<0.01	0.61	<0.01	10.69	2.53
631657	Drill Core	<0.01	0.68	<0.01	8.63	2.45
631658	Drill Core	<0.01	0.12	<0.01	0.80	2.39
631659	Drill Core	<0.01	0.24	<0.01	0.85	2.40
631660	Drill Core	<0.01	0.18	<0.01	17.00	2.90
631661	Drill Core	<0.01	0.17	<0.01	16.28	2.90
631662	Drill Core	<0.01	0.15	<0.01	3.70	2.52
631663	Drill Core	<0.01	0.21	<0.01	3.55	2.45
631664	Drill Core	<0.01	0.36	<0.01	1.23	2.51
631665	Drill Core	<0.01	0.60	<0.01	0.90	2.34
631666	Drill Core	<0.01	0.54	<0.01	0.97	2.36
631667	Drill Core	<0.01	0.72	<0.01	0.94	2.28
631668	Drill Core	<0.01	0.74	<0.01	0.80	2.23
631669	Drill Core	<0.01	0.59	<0.01	1.26	2.45
631670	Rock	<0.01	0.02	<0.01	<0.05	2.60
631671	Drill Core	<0.01	0.48	<0.01	1.20	2.22
631672	Drill Core	<0.01	0.56	<0.01	10.65	2.55
631673	Drill Core	<0.01	0.24	<0.01	11.34	2.81
631674	Drill Core	<0.01	0.14	<0.01	12.87	2.81
631675	Drill Core	<0.01	0.50	<0.01	2.54	2.41
631676	Drill Core	<0.01	0.52	<0.01	5.58	2.44
631677	Drill Core	<0.01	0.61	<0.01	14.07	2.56
631678	Drill Core	<0.01	0.68	<0.01	14.34	2.61
631679	Drill Core	0.02	0.19	<0.01	2.99	2.47
631680	Rock Pulp	2.29	1.39	<0.01	4.86	N.A.



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: Selwyn Resources Ltd.
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: January 14, 2011

Page: 3 of 3 **Part** 1

CERTIFICATE OF ANALYSIS

WHI10000713.1

	Method Analyte Unit MDL	WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD
		Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg	Al
		kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%	%
		0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01	0.01
631681	Drill Core	1.91	0.002	0.004	0.18	0.61	<2	0.006	<0.001	0.02	2.86	<0.02	<0.01	0.001	<0.01	<0.01	7.64	0.04	0.003	0.08	0.63
631682	Drill Core	1.17	0.004	0.015	3.64	17.01	9	0.009	<0.001	0.05	6.59	<0.02	<0.01	0.047	0.01	<0.01	9.62	0.11	0.002	0.10	0.81
631683	Drill Core	2.58	<0.001	<0.001	0.54	0.43	3	0.003	<0.001	0.06	0.87	<0.02	0.02	0.001	<0.01	<0.01	25.42	0.04	<0.001	0.09	0.21
631684	Drill Core	1.76	0.002	0.005	<0.02	0.02	<2	0.014	<0.001	<0.01	2.24	<0.02	<0.01	<0.001	<0.01	<0.01	2.58	0.07	0.012	0.37	4.46
631685	Drill Core	2.59	0.003	0.006	<0.02	<0.01	2	0.016	<0.001	<0.01	2.32	<0.02	<0.01	<0.001	<0.01	<0.01	1.20	0.12	0.013	0.36	4.77
631686	Drill Core	2.69	0.003	0.007	<0.02	<0.01	<2	0.017	<0.001	<0.01	2.77	<0.02	<0.01	<0.001	<0.01	<0.01	2.11	0.10	0.013	0.36	4.79
631687	Drill Core	2.78	0.003	0.005	<0.02	0.01	3	0.017	<0.001	<0.01	2.25	<0.02	<0.01	<0.001	<0.01	<0.01	2.72	0.09	0.014	0.36	4.65
631688	Drill Core	1.67	0.004	0.006	0.07	0.26	3	0.014	<0.001	0.01	2.04	<0.02	<0.01	<0.001	<0.01	<0.01	4.95	0.22	0.009	0.28	3.16
631689	Drill Core	1.92	0.007	0.011	0.37	0.83	5	0.022	<0.001	<0.01	2.43	<0.02	<0.01	0.003	<0.01	<0.01	5.60	1.79	0.013	0.26	2.28
631690	Drill Core	0.70	0.005	0.007	0.30	0.60	3	0.021	<0.001	<0.01	1.09	<0.02	<0.01	0.002	<0.01	<0.01	6.31	1.94	0.011	0.23	2.07
631691	Drill Core	0.73	0.004	0.008	0.63	0.73	5	0.021	<0.001	<0.01	1.26	<0.02	<0.01	0.002	<0.01	<0.01	7.00	2.33	0.014	0.25	2.07
631692	Drill Core	2.07	<0.001	0.004	0.02	<0.01	<2	0.005	<0.001	0.03	2.26	<0.02	0.01	<0.001	<0.01	<0.01	16.73	0.05	0.003	0.31	2.74
631693	Drill Core	0.99	<0.001	0.002	<0.02	<0.01	<2	0.002	<0.001	0.04	1.21	<0.02	0.02	<0.001	<0.01	<0.01	28.75	0.02	0.003	0.28	2.05
631694	Drill Core	1.29	0.003	0.006	<0.02	<0.01	<2	0.010	<0.001	0.04	2.31	<0.02	0.01	<0.001	<0.01	<0.01	20.53	0.10	0.007	0.26	2.66



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: January 14, 2011

Page: 3 of 3 **Part** 2

CERTIFICATE OF ANALYSIS

WHI10000713.1

	Method	7TD	7TD	7TD	7TD	G8SG
	Analyte	Na	K	W	S	SG
	Unit	%	%	%	%	
	MDL	0.01	0.01	0.01	0.05	0
631681	Drill Core	<0.01	0.41	<0.01	3.32	2.41
631682	Drill Core	<0.01	0.50	<0.01	16.01	2.71
631683	Drill Core	<0.01	0.12	<0.01	1.11	2.50
631684	Drill Core	0.02	3.45	<0.01	2.30	2.30
631685	Drill Core	0.02	3.48	<0.01	2.47	2.22
631686	Drill Core	0.02	3.52	<0.01	2.92	2.25
631687	Drill Core	0.02	3.56	<0.01	2.39	2.25
631688	Drill Core	0.01	2.28	<0.01	2.25	2.16
631689	Drill Core	<0.01	1.31	<0.01	3.07	1.90
631690	Drill Core	<0.01	1.28	<0.01	1.42	1.86
631691	Drill Core	<0.01	1.24	<0.01	1.73	1.89
631692	Drill Core	<0.01	1.67	<0.01	2.45	2.48
631693	Drill Core	<0.01	1.19	<0.01	1.29	2.53
631694	Drill Core	<0.01	1.44	<0.01	2.50	2.29



Acme Analytical Laboratories (Vancouver) Ltd.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: Selwyn Resources Ltd.

Suite 700 - 509 Richards Street

Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: January 14, 2011

Page: 1 of 1 Part 1

QUALITY CONTROL REPORT

WHI10000713.1

	Method Analyte Unit MDL	WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD
		Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg	Al
		kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%	%
		0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01	0.01
Core Reject Duplicates																					
631681	Drill Core	1.91	0.002	0.004	0.18	0.61	<2	0.006	<0.001	0.02	2.86	<0.02	<0.01	0.001	<0.01	<0.01	7.64	0.04	0.003	0.08	0.63
DUP 631681	QC		0.003	0.005	0.16	0.57	<2	0.007	<0.001	0.02	3.74	<0.02	<0.01	0.001	<0.01	<0.01	6.31	0.05	0.002	0.09	0.71
Reference Materials																					
STD OREAS131A	Standard		<0.001	0.032	1.70	2.89	31	0.004	0.002	0.17	5.74	<0.02	<0.01	0.008	<0.01	<0.01	5.29	0.06	0.002	3.17	4.71
STD OREAS131A	Standard		<0.001	0.032	1.75	2.86	32	0.002	0.002	0.17	5.93	<0.02	<0.01	0.008	<0.01	<0.01	5.31	0.06	0.003	3.14	4.61
STD OREAS131A	Standard		<0.001	0.033	1.73	2.92	31	0.003	0.003	0.18	5.94	<0.02	<0.01	0.008	<0.01	<0.01	5.46	0.06	0.003	3.15	4.60
STD OREAS131A	Standard		0.001	0.032	1.71	2.85	31	0.003	0.002	0.17	5.86	<0.02	<0.01	0.008	<0.01	<0.01	5.37	0.06	0.002	3.11	4.58
STD R4T	Standard		0.063	0.507	1.56	3.44	89	0.354	0.040	0.09	23.95	<0.02	0.02	0.018	0.02	<0.01	2.19	0.05	0.020	1.43	4.00
STD R4T	Standard		0.063	0.500	1.52	3.39	88	0.349	0.041	0.09	24.09	<0.02	0.02	0.018	0.02	<0.01	2.15	0.05	0.018	1.38	3.89
STD R4T	Standard		0.066	0.523	1.61	3.47	89	0.360	0.045	0.09	24.70	<0.02	0.02	0.019	0.02	<0.01	2.25	0.05	0.019	1.45	4.00
STD R4T	Standard		0.069	0.514	1.59	3.42	91	0.357	0.043	0.09	24.45	<0.02	0.02	0.019	0.02	<0.01	2.19	0.06	0.018	1.43	3.95
STD SU-1B	Standard		<0.001	1.196	<0.02	0.03	7	2.019	0.067	0.07	25.46	<0.02	0.03	<0.001	<0.01	<0.01	2.28	0.06	0.032	1.85	4.53
STD SU-1B	Standard		<0.001	1.200	<0.02	0.04	8	2.000	0.069	0.07	25.60	<0.02	0.03	0.001	<0.01	<0.01	2.22	0.06	0.032	1.78	4.38
STD SU-1B	Standard		<0.001	1.200	<0.02	0.03	6	1.993	0.069	0.07	25.58	<0.02	0.03	<0.001	<0.01	<0.01	2.25	0.06	0.033	1.80	4.36
STD SU-1B	Standard		0.002	1.181	<0.02	0.03	7	1.997	0.069	0.07	25.67	<0.02	0.03	<0.001	<0.01	<0.01	2.24	0.07	0.033	1.80	4.36
STD R4T Expected			0.062	0.502	1.518	3.376	86	0.339	0.039	0.086	24.07	0.0087	0.0185	0.018	0.0138	0.0018	2.166	0.045	0.018	1.384	3.897
STD OREAS131A Expected			0.001	0.0322	1.72	2.83	30.9	0.0027	0.0023	0.1722	5.8166	0.0082	0.0028	0.0081	0.0047	0.001	5.286	0.0536	0.0025	3.1182	4.6057
STD SU-1B Expected			0.0004	1.185	0.0058	0.0235	6.4	1.97	0.0672	0.0703	25.54	0.00025	0.03	0.0003	0.00002	0.0003	2.21	0.06	0.032	1.79	4.39
BLK	Blank		<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	<0.01	<0.01	<0.02	<0.01	<0.001	<0.01	<0.01	<0.01	<0.01	<0.001	<0.01	<0.01
BLK	Blank		<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	<0.01	<0.01	<0.02	<0.01	<0.001	<0.01	<0.01	<0.01	<0.01	<0.001	<0.01	<0.01
BLK	Blank		<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	<0.01	<0.01	<0.02	<0.01	<0.001	<0.01	<0.01	<0.01	<0.01	<0.001	<0.01	<0.01
BLK	Blank		<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	<0.01	<0.01	<0.02	<0.01	<0.001	<0.01	<0.01	<0.01	<0.01	<0.001	<0.01	<0.01
Prep Wash																					
G1	Prep Blank		<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	0.08	2.52	<0.02	0.07	<0.001	<0.01	<0.01	2.46	0.08	<0.001	0.63	7.31
G1	Prep Blank		<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	0.07	2.45	<0.02	0.07	<0.001	<0.01	<0.01	2.39	0.08	0.001	0.62	7.40



Acme Analytical Laboratories (Vancouver) Ltd.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: Selwyn Resources Ltd.

Suite 700 - 509 Richards Street

Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: January 14, 2011

Page: 1 of 1 Part 2

QUALITY CONTROL REPORT

WHI10000713.1

Method		7TD	7TD	7TD	7TD	G8SG
Analyte		Na	K	W	S	SG
Unit		%	%	%	%	%
MDL		0.01	0.01	0.01	0.05	0
Core Reject Duplicates						
631681	Drill Core	<0.01	0.41	<0.01	3.32	2.41
DUP 631681	QC	<0.01	0.46	<0.01	4.33	2.39
Reference Materials						
STD OREAS131A	Standard	0.16	3.43	<0.01	4.70	
STD OREAS131A	Standard	0.15	3.33	<0.01	4.68	
STD OREAS131A	Standard	0.16	3.46	<0.01	4.64	
STD OREAS131A	Standard	0.15	3.36	<0.01	4.74	
STD R4T	Standard	0.92	1.17	<0.01	11.37	
STD R4T	Standard	0.89	1.09	<0.01	10.83	
STD R4T	Standard	0.95	1.22	<0.01	11.77	
STD R4T	Standard	0.94	1.20	<0.01	12.10	
STD SU-1B	Standard	1.75	0.62	<0.01	8.07	
STD SU-1B	Standard	1.68	0.61	<0.01	8.41	
STD SU-1B	Standard	1.75	0.63	<0.01	7.56	
STD SU-1B	Standard	1.71	0.63	<0.01	8.08	
STD R4T Expected		0.9	1.153	0.00016	12.9903	
STD OREAS131A Expected		0.1501	3.1584	0.0005	4.8	
STD SU-1B Expected		1.662	0.6	0.0007	8.76	
BLK	Blank	<0.01	<0.01	<0.01	<0.05	
BLK	Blank	<0.01	<0.01	<0.01	<0.05	
BLK	Blank	<0.01	<0.01	<0.01	<0.05	
BLK	Blank	<0.01	<0.01	<0.01	<0.05	
Prep Wash						
G1	Prep Blank	2.77	1.74	<0.01	0.05	2.70
G1	Prep Blank	2.72	1.34	<0.01	<0.05	2.71



1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**

Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Submitted By: Jason K. Dunning

Receiving Lab: Canada-Whitehorse

Received: December 22, 2010

Report Date: January 12, 2011

Page: 1 of 2

CERTIFICATE OF ANALYSIS

WHI10000712.1

CLIENT JOB INFORMATION

Project: Selwyn Project
Shipment ID:
P.O. Number 1175
Number of Samples: 26

SAMPLE DISPOSAL

STOR-PLP Store After 90 days Invoice for Storage
STOR-RJT Store After 90 days Invoice for Storage

Acme does not accept responsibility for samples left at the laboratory after 90 days without prior written instructions for sample storage or return.

Invoice To: Selwyn Resources Ltd.
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6
Canada

CC:

SAMPLE PREPARATION AND ANALYTICAL PROCEDURES

Method Code	Number of Samples	Code Description	Test Wgt (g)	Report Status	Lab
R200-250	24	Crush split and pulverize 250g drill core to 200 mesh			WHI
7TD2	26	4 Acid digestion ICP-ES analysis.	0.5	Completed	VAN
G812	26	Specific Gravity on Pulp		Completed	VAN

ADDITIONAL COMMENTS



This report supersedes all previous preliminary and final reports with this file number dated prior to the date on this certificate. Signature indicates final approval; preliminary reports are unsigned and should be used for reference only.
All results are considered the confidential property of the client. Acme assumes the liabilities for actual cost of analysis only.
** asterisk indicates that an analytical result could not be provided due to unusually high levels of interference from other elements.



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: January 12, 2011

Page: 2 of 2 Part 1

CERTIFICATE OF ANALYSIS

WHI10000712.1

	Method Analyte Unit MDL	WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	
		Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg	Al
		kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%	%
		0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01	0.01
635251	Drill Core	1.18	<0.001	0.002	0.50	0.99	<2	0.003	<0.001	0.09	3.34	<0.02	0.01	0.003	<0.01	<0.01	27.96	0.03	<0.001	0.11	0.24
635252	Drill Core	0.74	0.002	0.004	0.45	6.96	<2	0.007	<0.001	0.02	2.50	<0.02	<0.01	0.016	<0.01	<0.01	6.92	0.05	0.001	0.07	0.61
635253	Drill Core	0.54	<0.001	<0.001	0.06	0.12	<2	0.003	<0.001	0.08	0.37	<0.02	0.02	<0.001	<0.01	<0.01	34.73	0.02	<0.001	0.11	0.08
635254	Drill Core	0.92	0.001	0.002	0.07	0.15	<2	0.007	<0.001	0.02	1.51	<0.02	<0.01	<0.001	<0.01	<0.01	8.58	0.03	0.003	0.12	1.10
635255	Drill Core	1.93	0.002	0.004	<0.02	0.02	2	0.013	<0.001	<0.01	2.04	<0.02	<0.01	<0.001	<0.01	<0.01	2.04	0.06	0.010	0.30	4.10
635256	Drill Core	2.00	0.007	0.005	<0.02	0.48	<2	0.018	<0.001	<0.01	1.92	<0.02	<0.01	0.003	<0.01	<0.01	1.00	0.09	0.010	0.29	3.99
635257	Drill Core	0.60	0.003	0.010	0.06	0.77	9	0.016	<0.001	0.07	2.15	<0.02	0.02	0.005	<0.01	<0.01	2.67	0.28	0.009	0.31	3.70
635258	Drill Core	2.15	0.005	0.006	<0.02	0.48	3	0.017	<0.001	0.01	2.08	<0.02	<0.01	0.003	<0.01	<0.01	2.22	0.08	0.010	0.29	3.71
635259	Drill Core	2.52	0.005	0.014	0.12	0.37	4	0.014	<0.001	<0.01	3.68	<0.02	<0.01	0.001	<0.01	<0.01	3.63	0.16	0.008	0.21	2.47
635260	Drill Core	0.98	0.007	0.009	0.06	0.61	2	0.017	<0.001	<0.01	0.85	<0.02	<0.01	0.002	<0.01	<0.01	4.26	0.84	0.007	0.17	1.57
635261	Drill Core	1.04	0.007	0.010	0.11	0.57	4	0.017	<0.001	<0.01	0.88	<0.02	<0.01	0.002	<0.01	<0.01	4.82	0.88	0.007	0.18	1.58
635262	Drill Core	3.11	<0.001	0.002	<0.02	<0.01	<2	0.004	<0.001	0.03	2.10	<0.02	0.01	<0.001	<0.01	<0.01	15.47	0.04	0.003	0.34	2.83
635263	Drill Core	2.92	<0.001	0.001	<0.02	<0.01	<2	0.003	<0.001	0.04	1.59	<0.02	0.02	<0.001	<0.01	<0.01	22.34	0.03	0.001	0.30	2.28
635264	Drill Core	1.67	0.001	0.005	<0.02	<0.01	<2	0.008	<0.001	0.04	2.53	<0.02	0.01	<0.001	<0.01	<0.01	17.86	0.07	0.004	0.43	3.76
635265	Drill Core	1.37	0.002	0.008	<0.02	0.01	<2	0.011	<0.001	0.03	2.05	<0.02	0.02	<0.001	<0.01	<0.01	15.81	0.33	0.006	0.31	3.02
635266	Drill Core	1.48	0.004	0.006	<0.02	0.68	2	0.013	<0.001	0.02	1.58	<0.02	<0.01	0.003	<0.01	<0.01	9.98	0.17	0.007	0.28	2.81
635267	Drill Core	1.13	<0.001	0.004	<0.02	0.13	<2	0.004	<0.001	0.05	1.03	<0.02	0.02	<0.001	<0.01	<0.01	28.59	0.15	<0.001	0.12	0.15
635268	Drill Core	1.60	0.003	0.006	0.17	0.29	<2	0.007	<0.001	0.03	0.86	<0.02	0.01	<0.001	<0.01	<0.01	18.49	0.26	0.002	0.10	0.55
635269	Drill Core	1.83	0.005	0.030	0.21	0.93	2	0.013	<0.001	0.01	7.41	<0.02	<0.01	0.003	<0.01	<0.01	7.41	0.18	0.004	0.12	0.80
635270	Rock	0.32	<0.001	<0.001	<0.02	<0.01	<2	0.002	<0.001	0.02	0.21	<0.02	0.01	<0.001	<0.01	<0.01	20.06	0.04	<0.001	10.82	0.15
635271	Drill Core	1.99	0.006	0.011	0.35	1.28	4	0.013	<0.001	0.01	1.67	<0.02	<0.01	0.004	<0.01	<0.01	8.88	0.27	0.004	0.12	0.97
635272	Drill Core	0.63	0.006	0.008	0.14	0.91	4	0.012	<0.001	0.02	0.44	<0.02	<0.01	0.003	<0.01	<0.01	12.50	0.36	0.003	0.11	0.87
635273	Drill Core	0.89	0.009	0.032	0.35	0.92	5	0.020	<0.001	<0.01	8.43	<0.02	<0.01	0.003	<0.01	<0.01	2.80	0.19	0.006	0.16	1.31
635274	Rock Pulp	0.05	<0.001	0.675	6.23	6.78	72	0.002	0.001	0.10	4.89	<0.02	0.02	0.019	0.04	<0.01	1.42	0.02	0.001	0.26	5.46
635275	Drill Core	1.30	0.005	0.012	<0.02	<0.01	2	0.026	<0.001	<0.01	3.16	<0.02	<0.01	<0.001	<0.01	<0.01	3.26	0.65	0.012	0.45	4.83
635276	Rock Pulp	0.05	<0.001	0.477	1.41	2.95	18	0.002	<0.001	0.45	2.62	<0.02	0.02	0.018	<0.01	<0.01	4.85	0.02	0.001	0.32	4.34



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**

Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: January 12, 2011

Page: 2 of 2 **Part** 2

CERTIFICATE OF ANALYSIS

WHI10000712.1

	Method	7TD	7TD	7TD	7TD	G8SG
	Analyte	Na	K	W	S	SG
	Unit	%	%	%	%	
	MDL	0.01	0.01	0.01	0.05	0
635251	Drill Core	0.01	0.14	<0.01	4.37	2.63
635252	Drill Core	<0.01	0.40	<0.01	6.48	2.60
635253	Drill Core	<0.01	0.04	<0.01	0.45	2.50
635254	Drill Core	<0.01	0.71	<0.01	1.61	2.47
635255	Drill Core	0.02	3.34	<0.01	2.10	2.40
635256	Drill Core	0.02	3.05	<0.01	2.25	2.18
635257	Drill Core	0.40	1.95	<0.01	2.01	1.61
635258	Drill Core	0.03	2.75	<0.01	2.37	2.07
635259	Drill Core	0.01	1.87	<0.01	4.36	2.62
635260	Drill Core	<0.01	1.04	<0.01	1.13	2.38
635261	Drill Core	<0.01	0.93	<0.01	1.11	2.21
635262	Drill Core	<0.01	1.75	<0.01	2.27	2.59
635263	Drill Core	<0.01	1.33	<0.01	1.69	2.62
635264	Drill Core	<0.01	2.31	<0.01	2.74	2.64
635265	Drill Core	<0.01	2.05	<0.01	2.18	2.45
635266	Drill Core	<0.01	1.94	<0.01	1.94	2.39
635267	Drill Core	<0.01	0.08	<0.01	1.16	2.59
635268	Drill Core	<0.01	0.27	<0.01	1.00	2.48
635269	Drill Core	<0.01	0.45	<0.01	8.79	2.57
635270	Rock	<0.01	0.03	<0.01	<0.05	2.75
635271	Drill Core	<0.01	0.55	<0.01	2.44	2.39
635272	Drill Core	<0.01	0.49	<0.01	0.83	2.36
635273	Drill Core	<0.01	0.72	<0.01	9.80	2.35
635274	Rock Pulp	2.33	1.37	<0.01	5.12	N.A.
635275	Drill Core	<0.01	3.06	<0.01	3.31	2.18
635276	Rock Pulp	1.78	1.27	<0.01	3.06	N.A.



Acme Analytical Laboratories (Vancouver) Ltd.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: **Selwyn Resources Ltd.**

Suite 700 - 509 Richards Street

Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: January 12, 2011

Page: 1 of 1 Part 1

QUALITY CONTROL REPORT

WHI10000712.1

	Method Analyte Unit MDL	WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD
		Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg	Al
		kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%	%
		0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01	0.01
Pulp Duplicates																					
635267	Drill Core	1.13	<0.001	0.004	<0.02	0.13	<2	0.004	<0.001	0.05	1.03	<0.02	0.02	<0.001	<0.01	<0.01	28.59	0.15	<0.001	0.12	0.15
REP 635267	QC		<0.001	0.004	<0.02	0.13	3	0.004	<0.001	0.05	1.01	<0.02	0.02	<0.001	<0.01	<0.01	27.88	0.14	<0.001	0.12	0.14
Reference Materials																					
STD OREAS131A	Standard		<0.001	0.032	1.70	2.89	31	0.004	0.002	0.17	5.74	<0.02	<0.01	0.008	<0.01	<0.01	5.29	0.06	0.002	3.17	4.71
STD OREAS131A	Standard		<0.001	0.032	1.70	2.90	31	0.003	0.003	0.17	5.88	<0.02	<0.01	0.008	<0.01	<0.01	5.37	0.05	0.002	3.05	4.57
STD R4T	Standard		0.063	0.507	1.56	3.44	89	0.354	0.040	0.09	23.95	<0.02	0.02	0.018	0.02	<0.01	2.19	0.05	0.020	1.43	4.00
STD R4T	Standard		0.064	0.513	1.54	3.47	88	0.352	0.042	0.09	24.41	<0.02	0.02	0.019	0.01	<0.01	2.22	0.06	0.018	1.40	3.91
STD SU-1B	Standard		<0.001	1.196	<0.02	0.03	7	2.019	0.067	0.07	25.46	<0.02	0.03	<0.001	<0.01	<0.01	2.28	0.06	0.032	1.85	4.53
STD SU-1B	Standard		<0.001	1.184	<0.02	0.02	7	1.979	0.069	0.07	25.43	<0.02	0.03	<0.001	<0.01	<0.01	2.22	0.06	0.031	1.76	4.31
STD R4T Expected			0.062	0.502	1.518	3.376	86	0.339	0.039	0.086	24.07	0.0087	0.0185	0.018	0.0138	0.0018	2.166	0.045	0.018	1.384	3.897
STD OREAS131A Expected			0.001	0.0322	1.72	2.83	30.9	0.0027	0.0023	0.1722	5.8166	0.0082	0.0028	0.0081	0.0047	0.001	5.286	0.0536	0.0025	3.1182	4.6057
STD SU-1B Expected			0.0004	1.185	0.0058	0.0235	6.4	1.97	0.0672	0.0703	25.54	0.00025	0.03	0.0003	0.00002	0.0003	2.21	0.06	0.032	1.79	4.39
BLK	Blank		<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	<0.01	<0.01	<0.02	<0.01	<0.001	<0.01	<0.01	<0.01	<0.01	<0.001	<0.01	<0.01
BLK	Blank		<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	<0.01	<0.01	<0.02	<0.01	<0.001	<0.01	<0.01	<0.01	<0.01	<0.001	<0.01	<0.01
Prep Wash																					
G1	Prep Blank		<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	0.07	2.39	<0.02	0.07	<0.001	<0.01	<0.01	2.34	0.07	<0.001	0.62	6.86
G1	Prep Blank		<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	0.08	2.34	<0.02	0.07	<0.001	<0.01	<0.01	2.37	0.07	0.001	0.61	6.89



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**

Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: January 12, 2011

Page: 1 of 1 **Part** 2

QUALITY CONTROL REPORT

WHI10000712.1

Method		7TD	7TD	7TD	7TD	G8SG
Analyte		Na	K	W	S	SG
Unit		%	%	%	%	%
MDL		0.01	0.01	0.01	0.05	0
Pulp Duplicates						
635267	Drill Core	<0.01	0.08	<0.01	1.16	2.59
REP 635267	QC	<0.01	0.07	<0.01	1.14	
Reference Materials						
STD OREAS131A	Standard	0.16	3.43	<0.01	4.70	
STD OREAS131A	Standard	0.15	3.43	<0.01	4.60	
STD R4T	Standard	0.92	1.17	<0.01	11.37	
STD R4T	Standard	0.93	1.18	<0.01	11.52	
STD SU-1B	Standard	1.75	0.62	<0.01	8.07	
STD SU-1B	Standard	1.69	0.62	<0.01	8.25	
STD R4T Expected		0.9	1.153	0.00016	12.9903	
STD OREAS131A Expected		0.1501	3.1584	0.0005	4.8	
STD SU-1B Expected		1.662	0.6	0.0007	8.76	
BLK	Blank	<0.01	<0.01	<0.01	<0.05	
BLK	Blank	<0.01	<0.01	<0.01	<0.05	
Prep Wash						
G1	Prep Blank	2.70	3.08	<0.01	<0.05	2.74
G1	Prep Blank	2.72	3.08	<0.01	<0.05	2.71



1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: Selwyn Resources Ltd.

Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Submitted By: Jason K. Dunning

Receiving Lab: Canada-Whitehorse

Received: December 22, 2010

Report Date: January 17, 2011

Page: 1 of 2

CERTIFICATE OF ANALYSIS

WHI10000711.1

CLIENT JOB INFORMATION

Project: Selwyn Project
Shipment ID:
P.O. Number 1175
Number of Samples: 24

SAMPLE DISPOSAL

STOR-PLP Store After 90 days Invoice for Storage
STOR-RJT Store After 90 days Invoice for Storage

Acme does not accept responsibility for samples left at the laboratory after 90 days without prior written instructions for sample storage or return.

Invoice To: Selwyn Resources Ltd.
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6
Canada

CC:

SAMPLE PREPARATION AND ANALYTICAL PROCEDURES

Method Code	Number of Samples	Code Description	Test Wgt (g)	Report Status	Lab
R200-250	24	Crush split and pulverize 250g drill core to 200 mesh			WHI
7TD2	24	4 Acid digestion ICP-ES analysis.	0.5	Completed	VAN
G812	24	Specific Gravity on Pulp		Completed	VAN
7TD.1	5	4 Acid digestion ICP-ES analysis	0.1	Completed	VAN

ADDITIONAL COMMENTS



This report supersedes all previous preliminary and final reports with this file number dated prior to the date on this certificate. Signature indicates final approval; preliminary reports are unsigned and should be used for reference only.
All results are considered the confidential property of the client. Acme assumes the liabilities for actual cost of analysis only.
** asterisk indicates that an analytical result could not be provided due to unusually high levels of interference from other elements.



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**

Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: January 17, 2011

Page: 2 of 2 Part 1

CERTIFICATE OF ANALYSIS

WHI10000711.1

	Method Analyte Unit MDL	WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD
		Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg
		kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%
		0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01
635051	Drill Core	1.34	<0.001	0.003	<0.02	0.11	<2	0.006	<0.001	<0.01	0.65	<0.02	<0.01	<0.001	<0.01	<0.01	2.94	0.90	0.005	0.08
635052	Drill Core	1.80	<0.001	0.005	0.12	0.61	<2	0.008	<0.001	<0.01	0.69	<0.02	<0.01	0.002	<0.01	<0.01	2.91	1.00	0.005	0.09
635053	Drill Core	1.44	<0.001	0.002	0.04	0.39	<2	0.004	<0.001	<0.01	0.99	<0.02	<0.01	0.001	<0.01	<0.01	2.81	0.89	0.005	0.07
635054	Drill Core	1.09	<0.001	0.002	>10	10.45	<2	0.002	<0.001	0.02	7.94	<0.02	<0.01	0.061	<0.01	<0.01	10.35	0.05	0.003	0.04
635055	Drill Core	1.74	<0.001	0.002	>10	20.40	3	<0.001	<0.001	0.02	0.50	<0.02	<0.01	0.115	<0.01	<0.01	13.76	<0.01	0.004	0.03
635056	Drill Core	1.99	<0.001	0.006	>10	27.07	10	0.002	<0.001	<0.01	1.51	<0.02	<0.01	0.153	<0.01	<0.01	5.90	0.03	0.004	0.02
635057	Drill Core	2.69	<0.001	0.004	>10	24.47	9	0.002	<0.001	<0.01	0.53	<0.02	<0.01	0.157	<0.01	<0.01	6.08	0.02	0.005	0.01
635058	Drill Core	1.39	<0.001	0.006	>10	26.89	11	0.004	<0.001	<0.01	2.39	<0.02	<0.01	0.155	<0.01	<0.01	3.21	0.03	0.005	0.03
635059	Drill Core	1.32	0.001	0.004	7.41	12.67	3	0.004	<0.001	0.03	2.56	<0.02	<0.01	0.060	<0.01	<0.01	14.81	0.03	0.002	0.18
635060	Drill Core	0.57	0.003	0.007	6.21	9.87	3	0.009	<0.001	0.02	3.62	<0.02	<0.01	0.047	<0.01	<0.01	9.18	0.07	0.004	0.13
635061	Drill Core	0.60	0.003	0.007	5.02	8.04	3	0.010	<0.001	0.02	3.78	<0.02	<0.01	0.038	<0.01	<0.01	9.81	0.06	0.004	0.14
635062	Drill Core	0.87	0.001	0.002	0.13	0.19	<2	0.006	<0.001	<0.01	0.68	<0.02	<0.01	<0.001	<0.01	<0.01	3.05	0.06	0.003	0.07
635063	Drill Core	1.50	<0.001	0.001	0.39	0.39	<2	0.004	<0.001	0.01	0.47	<0.02	<0.01	0.002	<0.01	<0.01	5.33	0.04	0.003	0.06
635064	Drill Core	0.59	<0.001	0.002	0.05	0.42	<2	0.003	<0.001	<0.01	0.53	<0.02	<0.01	0.001	<0.01	<0.01	1.05	0.03	0.003	0.05
635065	Drill Core	0.84	0.001	0.004	0.17	1.09	<2	0.006	<0.001	<0.01	1.15	<0.02	<0.01	0.003	<0.01	<0.01	1.89	0.02	0.003	0.06
635066	Drill Core	1.38	0.001	0.005	0.25	0.56	<2	0.005	<0.001	0.04	0.62	<0.02	0.02	0.002	<0.01	<0.01	26.33	0.10	0.002	0.10
635067	Drill Core	0.69	0.003	0.008	0.57	0.63	<2	0.005	<0.001	0.04	1.01	<0.02	0.02	0.002	<0.01	<0.01	25.49	1.31	0.002	0.08
635068	Drill Core	1.27	0.004	0.005	0.46	1.82	<2	0.007	<0.001	0.03	1.68	<0.02	0.02	0.005	<0.01	<0.01	25.43	0.23	0.003	0.15
635069	Drill Core	1.26	0.003	0.005	1.68	0.78	5	0.007	<0.001	0.01	0.46	<0.02	<0.01	0.002	<0.01	<0.01	8.11	0.37	0.004	0.08
635070	Rock	0.36	<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	0.02	0.16	<0.02	0.01	<0.001	<0.01	<0.01	21.47	0.03	<0.001	11.25
635071	Drill Core	1.04	0.003	0.017	0.61	0.42	5	0.026	<0.001	0.01	3.23	<0.02	<0.01	0.002	<0.01	<0.01	8.32	2.57	0.015	0.25
635072	Drill Core	1.90	<0.001	0.003	0.03	<0.01	<2	0.003	<0.001	0.04	2.01	<0.02	0.02	<0.001	<0.01	<0.01	23.33	0.05	0.003	0.37
635073	Drill Core	1.83	<0.001	0.003	<0.02	<0.01	<2	0.007	<0.001	0.04	1.94	<0.02	0.02	<0.001	<0.01	<0.01	23.26	0.04	0.003	0.45
635074	Drill Core	1.62	0.005	0.013	0.04	0.08	2	0.027	0.001	0.02	4.32	<0.02	0.01	<0.001	<0.01	<0.01	7.88	0.54	0.013	0.53



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**

Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: January 17, 2011

Page: 2 of 2 Part 2

CERTIFICATE OF ANALYSIS

WHI10000711.1

	Method Analyte Unit MDL	7TD	7TD	7TD	7TD	G8SG	7TD.1
		Na	K	W	S	SG	Pb
		%	%	%	%		%
		0.01	0.01	0.01	0.05	0	0.02
635051	Drill Core	<0.01	0.57	<0.01	0.48	2.29	
635052	Drill Core	<0.01	0.75	<0.01	0.92	2.16	
635053	Drill Core	<0.01	0.76	<0.01	0.97	2.35	
635054	Drill Core	<0.01	0.15	<0.01	15.24	3.12	11.93
635055	Drill Core	<0.01	0.02	<0.01	12.26	3.26	16.68
635056	Drill Core	<0.01	0.06	<0.01	17.89	3.52	26.89
635057	Drill Core	<0.01	0.03	<0.01	15.48	3.48	24.60
635058	Drill Core	<0.01	0.11	<0.01	18.47	3.91	24.84
635059	Drill Core	<0.01	0.19	<0.01	9.94	2.93	
635060	Drill Core	<0.01	0.79	<0.01	9.51	2.69	
635061	Drill Core	<0.01	0.80	<0.01	8.70	2.64	
635062	Drill Core	<0.01	0.38	<0.01	0.59	2.44	
635063	Drill Core	<0.01	0.22	<0.01	0.49	2.54	
635064	Drill Core	<0.01	0.21	<0.01	0.40	2.49	
635065	Drill Core	<0.01	0.29	<0.01	1.54	2.56	
635066	Drill Core	<0.01	0.32	<0.01	0.94	2.43	
635067	Drill Core	<0.01	0.17	<0.01	1.43	2.46	
635068	Drill Core	<0.01	0.29	<0.01	2.82	2.51	
635069	Drill Core	<0.01	0.31	<0.01	0.87	2.35	
635070	Rock	0.01	0.03	<0.01	<0.05	2.61	
635071	Drill Core	<0.01	1.43	<0.01	3.65	2.16	
635072	Drill Core	<0.01	1.49	<0.01	2.15	2.65	
635073	Drill Core	<0.01	2.02	<0.01	1.98	2.50	
635074	Drill Core	<0.01	3.22	<0.01	4.57	2.17	



Acme Analytical Laboratories (Vancouver) Ltd.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: Selwyn Resources Ltd.

Suite 700 - 509 Richards Street

Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: January 17, 2011

Page: 1 of 1 Part 1

QUALITY CONTROL REPORT

WHI10000711.1

Method Analyte Unit MDL	WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD
	Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg	Al
	kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%	%
	0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01	0.01
Pulp Duplicates																				
635055 Drill Core	1.74	<0.001	0.002	>10	20.40	3	<0.001	<0.001	0.02	0.50	<0.02	<0.01	0.115	<0.01	<0.01	13.76	<0.01	0.004	0.03	0.04
REP 635055 QC																				
635063 Drill Core	1.50	<0.001	0.001	0.39	0.39	<2	0.004	<0.001	0.01	0.47	<0.02	<0.01	0.002	<0.01	<0.01	5.33	0.04	0.003	0.06	0.40
REP 635063 QC		<0.001	<0.001	0.37	0.39	<2	0.004	<0.001	0.01	0.46	<0.02	<0.01	0.002	<0.01	<0.01	5.28	0.04	0.003	0.06	0.40
Reference Materials																				
STD CCU-1C Standard																				
STD CZN-3 Standard																				
STD OREAS131A Standard		<0.001	0.032	1.70	2.90	31	0.003	0.003	0.17	5.88	<0.02	<0.01	0.008	<0.01	<0.01	5.37	0.05	0.002	3.05	4.57
STD PTC-1A Standard																				
STD R4T Standard		0.064	0.513	1.54	3.47	88	0.352	0.042	0.09	24.41	<0.02	0.02	0.019	0.01	<0.01	2.22	0.06	0.018	1.40	3.91
STD SARM 71 Standard																				
STD SU-1B Standard		<0.001	1.184	<0.02	0.02	7	1.979	0.069	0.07	25.43	<0.02	0.03	<0.001	<0.01	<0.01	2.22	0.06	0.031	1.76	4.31
STD R4T Expected		0.062	0.502	1.518	3.376	86	0.339	0.039	0.086	24.07	0.0087	0.0185	0.018	0.0138	0.0018	2.166	0.045	0.018	1.384	3.897
STD OREAS131A Expected		0.001	0.0322	1.72	2.83	30.9	0.0027	0.0023	0.1722	5.8166	0.0082	0.0028	0.0081	0.0047	0.001	5.286	0.0536	0.0025	3.1182	4.6057
STD SU-1B Expected		0.0004	1.185	0.0058	0.0235	6.4	1.97	0.0672	0.0703	25.54	0.00025	0.03	0.0003	0.00002	0.0003	2.21	0.06	0.032	1.79	4.39
STD CZN-3 Expected																				
STD CCU-1C Expected																				
STD PTC-1A Expected																				
BLK Blank		<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	<0.01	<0.01	<0.02	<0.01	<0.001	<0.01	<0.01	<0.01	<0.01	<0.001	<0.01	<0.01
BLK Blank																				
Prep Wash																				
G1 Prep Blank		<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	0.07	2.33	<0.02	0.07	<0.001	<0.01	<0.01	2.30	0.07	0.002	0.57	6.86
G1 Prep Blank		<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	0.07	2.40	<0.02	0.07	<0.001	<0.01	<0.01	2.35	0.08	0.001	0.62	6.89



Acme Analytical Laboratories (Vancouver) Ltd.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: Selwyn Resources Ltd.

Suite 700 - 509 Richards Street

Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: January 17, 2011

Page: 1 of 1 **Part** 2

QUALITY CONTROL REPORT

WHI10000711.1

Method		7TD	7TD	7TD	7TD	G8SG	7TD.1
Analyte		Na	K	W	S	SG	Pb
Unit		%	%	%	%		%
MDL		0.01	0.01	0.01	0.05	0	0.02
Pulp Duplicates							
635055	Drill Core	<0.01	0.02	<0.01	12.26	3.26	16.68
REP 635055	QC						16.82
635063	Drill Core	<0.01	0.22	<0.01	0.49	2.54	
REP 635063	QC	<0.01	0.22	<0.01	0.48		
Reference Materials							
STD CCU-1C	Standard						0.39
STD CZN-3	Standard						0.10
STD OREAS131A	Standard	0.15	3.43	<0.01	4.60		
STD PTC-1A	Standard						0.09
STD R4T	Standard	0.93	1.18	<0.01	11.52		
STD SARM 71	Standard						0.03
STD SU-1B	Standard	1.69	0.62	<0.01	8.25		
STD R4T Expected		0.9	1.153	0.00016	12.9903		
STD OREAS131A Expected		0.1501	3.1584	0.0005	4.8		
STD SU-1B Expected		1.662	0.6	0.0007	8.76		
STD CZN-3 Expected							0.113
STD CCU-1C Expected							0.34
STD PTC-1A Expected							0.05
BLK	Blank	<0.01	<0.01	<0.01	<0.05		
BLK	Blank						<0.02
Prep Wash							
G1	Prep Blank	2.73	3.00	<0.01	<0.05	2.64	
G1	Prep Blank	2.70	2.94	<0.01	<0.05	2.63	



1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**

Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Submitted By: Jason K. Dunning

Receiving Lab: Canada-Whitehorse

Received: December 21, 2010

Report Date: January 11, 2011

Page: 1 of 3

CERTIFICATE OF ANALYSIS

WHI10000709.1

CLIENT JOB INFORMATION

Project: Selwyn Project
Shipment ID:
P.O. Number 1167
Number of Samples: 42

SAMPLE DISPOSAL

STOR-PLP Store After 90 days Invoice for Storage
STOR-RJT Store After 90 days Invoice for Storage

Acme does not accept responsibility for samples left at the laboratory after 90 days without prior written instructions for sample storage or return.

Invoice To: Selwyn Resources Ltd.
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6
Canada

CC:

SAMPLE PREPARATION AND ANALYTICAL PROCEDURES

Method Code	Number of Samples	Code Description	Test Wgt (g)	Report Status	Lab
R200-250	40	Crush split and pulverize 250g drill core to 200 mesh			WHI
7TD2	42	4 Acid digestion ICP-ES analysis.	0.5	Completed	VAN
G812	42	Specific Gravity on Pulp		Completed	VAN

ADDITIONAL COMMENTS



This report supersedes all previous preliminary and final reports with this file number dated prior to the date on this certificate. Signature indicates final approval; preliminary reports are unsigned and should be used for reference only.
All results are considered the confidential property of the client. Acme assumes the liabilities for actual cost of analysis only.
** asterisk indicates that an analytical result could not be provided due to unusually high levels of interference from other elements.



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: January 11, 2011

Page: 2 of 3 Part 1

CERTIFICATE OF ANALYSIS

WHI10000709.1

	Method Analyte Unit MDL	WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD
		Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg	Al
		kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%	%
		0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01	0.01
633401	Drill Core	2.05	0.001	0.003	0.02	0.34	<2	0.005	<0.001	0.03	0.80	<0.02	<0.01	0.001	<0.01	<0.01	11.61	0.62	0.003	0.14	1.04
633402	Drill Core	1.81	0.002	0.005	0.71	0.72	<2	0.009	<0.001	<0.01	1.95	<0.02	<0.01	0.003	<0.01	<0.01	1.57	0.48	0.004	0.14	1.46
633403	Drill Core	2.44	0.002	0.007	0.94	1.40	<2	0.006	<0.001	0.02	7.70	<0.02	<0.01	0.007	<0.01	<0.01	9.48	0.03	0.003	0.08	0.82
633404	Drill Core	0.87	0.002	0.008	6.88	16.49	5	0.005	<0.001	<0.01	3.15	<0.02	<0.01	0.076	<0.01	<0.01	0.36	0.04	0.002	0.06	0.71
633405	Drill Core	1.63	0.003	0.005	0.57	3.52	<2	0.007	<0.001	0.02	3.56	<0.02	<0.01	0.008	<0.01	<0.01	4.91	0.04	0.003	0.07	0.84
633406	Drill Core	1.72	0.001	0.003	1.24	4.84	<2	0.003	<0.001	0.01	1.51	<0.02	<0.01	0.014	<0.01	<0.01	7.31	0.06	0.002	0.05	0.43
633407	Drill Core	0.68	<0.001	0.002	1.23	2.28	<2	0.003	<0.001	0.01	0.76	<0.02	<0.01	0.008	<0.01	<0.01	5.50	0.04	0.002	0.06	0.53
633408	Drill Core	0.93	0.001	0.001	1.37	1.68	<2	0.004	<0.001	0.05	0.56	<0.02	0.01	0.008	<0.01	<0.01	21.72	0.04	0.001	0.10	0.61
633409	Drill Core	1.41	0.002	0.001	0.08	1.19	<2	0.006	<0.001	<0.01	0.82	<0.02	<0.01	0.004	<0.01	<0.01	1.60	0.03	0.003	0.06	0.62
633410	Drill Core	0.68	0.004	0.004	0.13	0.60	<2	0.009	<0.001	<0.01	2.54	<0.02	<0.01	0.002	<0.01	<0.01	1.84	0.03	0.002	0.09	1.17
633411	Drill Core	0.67	0.004	0.006	0.12	0.45	<2	0.010	<0.001	<0.01	5.08	<0.02	<0.01	0.001	<0.01	<0.01	1.65	0.03	0.002	0.08	1.06
633412	Drill Core	1.16	0.004	0.009	1.82	11.11	<2	0.007	<0.001	0.02	4.17	<0.02	<0.01	0.028	<0.01	<0.01	3.63	0.07	0.003	0.07	0.79
633413	Drill Core	0.52	<0.001	<0.001	0.99	2.34	<2	<0.001	<0.001	0.07	0.39	<0.02	0.01	0.008	<0.01	<0.01	23.78	0.05	<0.001	0.11	0.12
633414	Drill Core	1.47	<0.001	<0.001	0.36	0.18	<2	<0.001	<0.001	0.06	1.53	<0.02	0.02	<0.001	<0.01	<0.01	31.03	0.04	<0.001	0.10	0.09
633415	Drill Core	2.10	<0.001	<0.001	0.85	0.75	<2	0.001	<0.001	0.05	2.68	<0.02	0.01	0.002	<0.01	<0.01	27.61	0.03	<0.001	0.08	0.13
633416	Drill Core	0.63	<0.001	<0.001	0.06	0.87	<2	0.002	<0.001	0.03	0.53	<0.02	<0.01	0.002	<0.01	<0.01	15.45	0.04	<0.001	0.07	0.24
633417	Drill Core	1.10	<0.001	<0.001	0.35	0.34	<2	<0.001	<0.001	0.06	0.41	<0.02	0.02	<0.001	<0.01	<0.01	36.60	0.03	<0.001	0.11	0.14
633418	Drill Core	1.25	<0.001	0.003	1.87	5.88	<2	0.004	<0.001	0.02	3.47	<0.02	<0.01	0.018	<0.01	<0.01	5.09	0.06	0.002	0.07	0.67
633419	Drill Core	2.19	0.001	0.002	1.47	4.59	<2	0.003	<0.001	0.05	2.38	<0.02	0.01	0.012	<0.01	<0.01	26.32	0.04	0.001	0.09	0.43
633420	Rock	0.36	<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	0.02	0.18	<0.02	0.01	<0.001	<0.01	<0.01	21.32	0.03	<0.001	11.26	0.20
633421	Drill Core	1.53	0.001	0.003	1.34	4.53	<2	0.004	<0.001	0.03	2.08	<0.02	<0.01	0.011	<0.01	<0.01	10.01	0.06	0.002	0.09	0.63
633422	Drill Core	2.47	0.001	0.003	1.22	6.71	<2	0.004	<0.001	0.03	1.63	<0.02	<0.01	0.019	<0.01	<0.01	11.31	0.04	0.002	0.07	0.45
633423	Drill Core	1.81	0.001	0.002	0.57	1.08	<2	0.005	<0.001	0.02	0.78	<0.02	<0.01	0.002	<0.01	<0.01	12.60	0.06	0.002	0.12	0.72
633424	Drill Core	2.95	<0.001	<0.001	<0.02	0.02	<2	0.002	<0.001	0.03	0.42	<0.02	0.01	<0.001	<0.01	<0.01	21.38	0.03	<0.001	0.08	0.42
633425	Drill Core	3.70	<0.001	0.003	<0.02	0.01	<2	0.003	<0.001	0.04	0.88	<0.02	0.01	<0.001	<0.01	<0.01	24.47	0.04	0.001	0.10	0.62
633426	Drill Core	1.54	0.001	0.004	0.18	<0.01	<2	0.004	<0.001	0.04	0.68	<0.02	0.01	<0.001	<0.01	<0.01	22.48	0.04	0.002	0.10	0.63
633427	Drill Core	0.42	0.002	0.006	0.08	<0.01	<2	0.008	<0.001	0.03	4.72	<0.02	<0.01	<0.001	<0.01	<0.01	10.57	0.06	0.003	0.15	1.12
633428	Drill Core	0.52	0.004	0.011	0.06	0.02	<2	0.012	<0.001	0.03	3.71	<0.02	<0.01	<0.001	<0.01	<0.01	11.93	0.11	0.003	0.18	1.42
633429	Drill Core	1.84	<0.001	0.002	<0.02	0.02	<2	0.004	<0.001	0.03	2.01	<0.02	0.01	<0.001	<0.01	<0.01	20.73	0.03	0.001	0.07	0.34
633430	Rock Pulp	0.06	<0.001	0.670	6.24	6.66	70	<0.001	0.001	0.09	4.64	<0.02	0.02	0.018	0.01	<0.01	1.29	0.02	0.001	0.24	4.51



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**

Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: January 11, 2011

Page: 2 of 3 **Part** 2

CERTIFICATE OF ANALYSIS

WHI10000709.1

	Method	7TD	7TD	7TD	7TD	G8SG
	Analyte	Na	K	W	S	SG
	Unit	%	%	%	%	
	MDL	0.01	0.01	0.01	0.05	0
633401	Drill Core	<0.01	0.63	<0.01	1.00	2.28
633402	Drill Core	<0.01	0.81	<0.01	2.61	2.23
633403	Drill Core	<0.01	0.50	<0.01	10.41	2.56
633404	Drill Core	<0.01	0.41	<0.01	12.94	2.77
633405	Drill Core	<0.01	0.52	<0.01	6.18	2.37
633406	Drill Core	<0.01	0.23	<0.01	4.22	2.38
633407	Drill Core	<0.01	0.27	<0.01	2.07	2.37
633408	Drill Core	<0.01	0.30	<0.01	1.66	2.41
633409	Drill Core	<0.01	0.33	<0.01	1.39	2.25
633410	Drill Core	<0.01	0.74	<0.01	3.12	2.16
633411	Drill Core	<0.01	0.67	<0.01	6.32	2.22
633412	Drill Core	<0.01	0.49	<0.01	10.85	2.49
633413	Drill Core	<0.01	0.06	<0.01	1.73	2.57
633414	Drill Core	<0.01	0.04	<0.01	1.99	2.56
633415	Drill Core	<0.01	0.06	<0.01	3.71	2.54
633416	Drill Core	<0.01	0.11	<0.01	1.05	2.41
633417	Drill Core	<0.01	0.07	<0.01	0.71	2.50
633418	Drill Core	<0.01	0.40	<0.01	7.52	2.50
633419	Drill Core	<0.01	0.19	<0.01	5.52	2.52
633420	Rock	0.01	0.04	<0.01	0.06	2.60
633421	Drill Core	<0.01	0.37	<0.01	4.97	2.45
633422	Drill Core	<0.01	0.24	<0.01	5.64	2.45
633423	Drill Core	<0.01	0.39	<0.01	1.51	2.32
633424	Drill Core	<0.01	0.19	<0.01	0.50	2.35
633425	Drill Core	<0.01	0.30	<0.01	1.06	2.35
633426	Drill Core	<0.01	0.32	<0.01	0.85	2.36
633427	Drill Core	<0.01	0.68	<0.01	6.03	2.32
633428	Drill Core	<0.01	0.81	<0.01	4.61	2.22
633429	Drill Core	<0.01	0.17	<0.01	2.45	2.40
633430	Rock Pulp	2.31	1.31	<0.01	5.71	N.A.



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: January 11, 2011

Page: 3 of 3 **Part** 1

CERTIFICATE OF ANALYSIS

WHI10000709.1

	Method Analyte Unit MDL	WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD
		Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg	Al
		kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%	%
		0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01	0.01
633431	Drill Core	2.12	0.003	0.007	0.04	0.15	<2	0.016	<0.001	0.01	1.94	<0.02	<0.01	<0.001	<0.01	<0.01	5.37	0.86	0.008	0.33	2.64
633432	Drill Core	3.40	<0.001	0.001	<0.02	<0.01	<2	0.003	<0.001	0.04	1.20	<0.02	0.02	<0.001	<0.01	<0.01	28.07	0.02	0.002	0.26	1.49
633433	Drill Core	1.77	0.002	0.003	<0.02	0.04	2	0.007	<0.001	0.03	3.17	<0.02	0.02	<0.001	<0.01	<0.01	20.46	2.43	0.003	0.28	2.10
633434	Drill Core	1.53	0.003	0.004	<0.02	0.01	2	0.014	<0.001	<0.01	2.40	<0.02	<0.01	<0.001	<0.01	<0.01	1.43	0.14	0.014	0.38	4.61
633435	Drill Core	1.09	0.004	0.006	<0.02	0.02	2	0.015	<0.001	0.02	1.96	<0.02	<0.01	<0.001	<0.01	<0.01	6.30	0.10	0.010	0.33	3.89
633436	Drill Core	0.92	0.004	0.005	<0.02	0.02	<2	0.016	<0.001	0.01	1.93	<0.02	<0.01	<0.001	<0.01	<0.01	3.66	0.11	0.010	0.35	4.20
633437	Rock	0.33	<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	0.02	0.25	<0.02	0.01	<0.001	<0.01	<0.01	20.45	0.03	<0.001	11.03	0.22
633438	Rock Pulp	0.06	<0.001	0.486	1.45	3.00	20	<0.001	<0.001	0.45	2.68	<0.02	0.02	0.018	<0.01	<0.01	4.86	0.02	0.001	0.32	4.37
633439	Drill Core	1.75	<0.001	0.009	<0.02	<0.01	<2	0.008	<0.001	0.02	2.57	<0.02	0.02	<0.001	<0.01	<0.01	11.94	0.83	0.007	1.32	2.45
633440	Drill Core	1.71	0.001	0.008	<0.02	0.20	<2	0.012	<0.001	0.01	1.75	<0.02	0.02	<0.001	<0.01	<0.01	7.57	1.56	0.009	1.26	3.79
633441	Drill Core	0.99	0.004	0.014	<0.02	0.45	3	0.013	<0.001	<0.01	2.55	<0.02	<0.01	0.002	<0.01	<0.01	2.49	0.40	0.008	1.35	4.58
633442	Drill Core	1.70	<0.001	0.005	<0.02	0.10	<2	0.007	<0.001	0.03	1.35	<0.02	0.02	<0.001	<0.01	<0.01	20.53	1.04	0.005	0.57	1.92



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**

Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: January 11, 2011

Page: 3 of 3 **Part** 2

CERTIFICATE OF ANALYSIS

WHI10000709.1

	Method	7TD	7TD	7TD	7TD	G8SG
	Analyte	Na	K	W	S	SG
	Unit	%	%	%	%	
	MDL	0.01	0.01	0.01	0.05	0
633431	Drill Core	<0.01	1.68	<0.01	2.32	2.48
633432	Drill Core	<0.01	0.79	<0.01	1.41	2.62
633433	Drill Core	0.01	1.46	<0.01	3.85	2.49
633434	Drill Core	0.01	3.56	<0.01	2.72	2.21
633435	Drill Core	0.01	3.02	<0.01	2.23	2.15
633436	Drill Core	0.01	3.29	<0.01	2.12	2.24
633437	Rock	<0.01	0.03	<0.01	0.10	2.60
633438	Rock Pulp	1.72	1.24	<0.01	3.31	N.A.
633439	Drill Core	<0.01	1.72	<0.01	2.70	2.23
633440	Drill Core	0.01	2.52	<0.01	1.83	2.26
633441	Drill Core	0.01	2.91	<0.01	2.89	2.07
633442	Drill Core	0.01	1.23	<0.01	1.48	2.30



Acme Analytical Laboratories (Vancouver) Ltd.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: Selwyn Resources Ltd.

Suite 700 - 509 Richards Street

Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: January 11, 2011

Page: 1 of 1 Part 1

QUALITY CONTROL REPORT

WHI10000709.1

	Method Analyte Unit MDL	WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD
		Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg	Al
		kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%	%
		0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01	0.01
Pulp Duplicates																					
633404	Drill Core	0.87	0.002	0.008	6.88	16.49	5	0.005	<0.001	<0.01	3.15	<0.02	<0.01	0.076	<0.01	<0.01	0.36	0.04	0.002	0.06	0.71
REP 633404	QC		0.002	0.008	6.87	16.44	5	0.005	<0.001	<0.01	3.15	<0.02	<0.01	0.076	<0.01	<0.01	0.37	0.04	0.001	0.06	0.71
633442	Drill Core	1.70	<0.001	0.005	<0.02	0.10	<2	0.007	<0.001	0.03	1.35	<0.02	0.02	<0.001	<0.01	<0.01	20.53	1.04	0.005	0.57	1.92
REP 633442	QC		<0.001	0.005	<0.02	0.10	2	0.007	<0.001	0.03	1.33	<0.02	0.02	<0.001	<0.01	<0.01	20.11	1.03	0.005	0.56	1.89
Core Reject Duplicates																					
633405	Drill Core	1.63	0.003	0.005	0.57	3.52	<2	0.007	<0.001	0.02	3.56	<0.02	<0.01	0.008	<0.01	<0.01	4.91	0.04	0.003	0.07	0.84
DUP 633405	QC		0.003	0.005	0.58	3.56	<2	0.007	<0.001	0.01	3.67	<0.02	<0.01	0.008	<0.01	<0.01	4.92	0.04	0.002	0.07	0.84
633440	Drill Core	1.71	0.001	0.008	<0.02	0.20	<2	0.012	<0.001	0.01	1.75	<0.02	0.02	<0.001	<0.01	<0.01	7.57	1.56	0.009	1.26	3.79
DUP 633440	QC		0.001	0.009	<0.02	0.21	3	0.012	<0.001	0.01	1.75	<0.02	0.02	<0.001	<0.01	<0.01	7.71	1.57	0.008	1.29	3.86
Reference Materials																					
STD OREAS131A	Standard		<0.001	0.032	1.74	2.94	31	0.003	0.002	0.17	5.75	<0.02	<0.01	0.008	<0.01	<0.01	5.24	0.06	0.002	3.19	4.71
STD OREAS131A	Standard		<0.001	0.032	1.71	2.85	31	0.002	0.002	0.17	5.76	<0.02	<0.01	0.008	<0.01	<0.01	5.19	0.05	0.002	3.12	4.65
STD R4T	Standard		0.063	0.509	1.56	3.48	86	0.353	0.040	0.09	24.15	<0.02	0.02	0.018	0.01	<0.01	2.21	0.05	0.018	1.43	3.98
STD R4T	Standard		0.064	0.519	1.59	3.48	90	0.358	0.041	0.09	24.33	<0.02	0.02	0.019	0.01	<0.01	2.20	0.05	0.020	1.44	4.01
STD SU-1B	Standard		<0.001	1.200	<0.02	0.02	6	2.011	0.067	0.07	25.71	<0.02	0.03	<0.001	<0.01	<0.01	2.26	0.06	0.030	1.82	4.47
STD SU-1B	Standard		<0.001	1.201	<0.02	0.03	7	2.008	0.068	0.07	25.25	<0.02	0.03	<0.001	<0.01	<0.01	2.25	0.06	0.032	1.80	4.44
STD R4T Expected			0.062	0.502	1.518	3.376	86	0.339	0.039	0.086	24.07	0.0087	0.0185	0.018	0.0138	0.0018	2.166	0.045	0.018	1.384	3.897
STD OREAS131A Expected			0.001	0.0322	1.72	2.83	30.9	0.0027	0.0023	0.1722	5.8166	0.0082	0.0028	0.0081	0.0047	0.001	5.286	0.0536	0.0025	3.1182	4.6057
STD SU-1B Expected			0.0004	1.185	0.0058	0.0235	6.4	1.97	0.0672	0.0703	25.54	0.00025	0.03	0.0003	0.00002	0.0003	2.21	0.06	0.032	1.79	4.39
BLK	Blank		<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	<0.01	<0.01	<0.02	<0.01	<0.001	<0.01	<0.01	<0.01	<0.01	<0.001	<0.01	<0.01
BLK	Blank		<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	<0.01	<0.01	<0.02	<0.01	<0.001	<0.01	<0.01	<0.01	<0.01	<0.001	<0.01	<0.01
Prep Wash																					
G1	Prep Blank		<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	0.07	2.21	<0.02	0.07	<0.001	<0.01	<0.01	2.34	0.08	0.002	0.57	6.82
G1	Prep Blank		<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	0.07	2.14	<0.02	0.07	<0.001	<0.01	<0.01	2.26	0.07	0.002	0.55	6.34



Acme Analytical Laboratories (Vancouver) Ltd.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: Selwyn Resources Ltd.

Suite 700 - 509 Richards Street

Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: January 11, 2011

Page: 1 of 1 **Part** 2

QUALITY CONTROL REPORT

WHI10000709.1

Method		7TD	7TD	7TD	7TD	G8SG
Analyte		Na	K	W	S	SG
Unit		%	%	%	%	%
MDL		0.01	0.01	0.01	0.05	0
Pulp Duplicates						
633404	Drill Core	<0.01	0.41	<0.01	12.94	2.77
REP 633404	QC	<0.01	0.41	<0.01	12.89	
633442	Drill Core	0.01	1.23	<0.01	1.48	2.30
REP 633442	QC	0.01	1.22	<0.01	1.45	
Core Reject Duplicates						
633405	Drill Core	<0.01	0.52	<0.01	6.18	2.37
DUP 633405	QC	<0.01	0.51	<0.01	6.36	2.36
633440	Drill Core	0.01	2.52	<0.01	1.83	2.26
DUP 633440	QC	0.01	2.57	<0.01	1.86	2.26
Reference Materials						
STD OREAS131A	Standard	0.15	3.45	<0.01	4.99	
STD OREAS131A	Standard	0.15	3.37	<0.01	4.92	
STD R4T	Standard	0.91	1.15	<0.01	12.93	
STD R4T	Standard	0.91	1.18	<0.01	12.91	
STD SU-1B	Standard	1.70	0.61	<0.01	10.86	
STD SU-1B	Standard	1.63	0.61	<0.01	8.88	
STD R4T Expected		0.9	1.153	0.00016	12.9903	
STD OREAS131A Expected		0.1501	3.1584	0.0005	4.8	
STD SU-1B Expected		1.662	0.6	0.0007	8.76	
BLK	Blank	<0.01	<0.01	<0.01	<0.05	
BLK	Blank	<0.01	<0.01	<0.01	<0.05	
Prep Wash						
G1	Prep Blank	2.75	3.02	<0.01	0.05	2.64
G1	Prep Blank	2.72	2.97	<0.01	<0.05	2.64



1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: Selwyn Resources Ltd.

Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Submitted By: Jason K. Dunning

Receiving Lab: Canada-Whitehorse

Received: December 21, 2010

Report Date: January 11, 2011

Page: 1 of 3

CERTIFICATE OF ANALYSIS

WHI10000708.1

CLIENT JOB INFORMATION

Project: Selwyn Project
Shipment ID:
P.O. Number 1167
Number of Samples: 32

SAMPLE DISPOSAL

STOR-PLP Store After 90 days Invoice for Storage
STOR-RJT Store After 90 days Invoice for Storage

Acme does not accept responsibility for samples left at the laboratory after 90 days without prior written instructions for sample storage or return.

Invoice To: Selwyn Resources Ltd.
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6
Canada

CC:

SAMPLE PREPARATION AND ANALYTICAL PROCEDURES

Method Code	Number of Samples	Code Description	Test Wgt (g)	Report Status	Lab
R200-250	31	Crush split and pulverize 250g drill core to 200 mesh			WHI
7TD2	32	4 Acid digestion ICP-ES analysis.	0.5	Completed	VAN
G812	32	Specific Gravity on Pulp		Completed	VAN

ADDITIONAL COMMENTS



This report supersedes all previous preliminary and final reports with this file number dated prior to the date on this certificate. Signature indicates final approval; preliminary reports are unsigned and should be used for reference only.
All results are considered the confidential property of the client. Acme assumes the liabilities for actual cost of analysis only.
** asterisk indicates that an analytical result could not be provided due to unusually high levels of interference from other elements.



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: January 11, 2011

Page: 2 of 3 Part 1

CERTIFICATE OF ANALYSIS

WHI10000708.1

	Method Analyte Unit MDL	WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD
		Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg	Al
		kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%	%
		0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01	0.01
633551	Drill Core	2.69	<0.001	0.004	<0.02	0.05	<2	0.008	<0.001	0.01	0.69	<0.02	<0.01	<0.001	<0.01	<0.01	8.84	1.08	0.005	0.18	1.87
633552	Drill Core	1.32	<0.001	0.004	1.59	3.74	3	0.004	<0.001	0.03	0.93	<0.02	0.01	0.011	<0.01	<0.01	15.66	0.08	0.003	0.09	0.45
633553	Drill Core	1.10	<0.001	<0.001	0.13	0.49	<2	<0.001	<0.001	0.06	0.22	<0.02	0.02	0.002	<0.01	<0.01	34.75	0.03	<0.001	0.10	0.07
633554	Drill Core	1.33	0.002	0.004	0.16	1.08	<2	0.010	<0.001	0.01	1.48	<0.02	<0.01	0.003	<0.01	<0.01	4.85	1.14	0.007	0.20	2.01
633555	Drill Core	1.50	0.002	0.005	1.02	4.09	3	0.006	<0.001	0.04	2.69	<0.02	0.01	0.012	<0.01	<0.01	18.77	0.08	0.003	0.12	0.73
633556	Drill Core	1.46	0.002	0.007	1.15	4.96	3	0.004	<0.001	0.04	2.54	<0.02	0.01	0.015	<0.01	<0.01	15.95	0.04	0.002	0.08	0.44
633557	Drill Core	1.12	0.001	0.001	0.10	0.36	<2	0.004	<0.001	0.01	0.65	<0.02	<0.01	0.001	<0.01	<0.01	6.96	0.02	0.003	0.05	0.32
633558	Drill Core	1.32	0.005	0.011	3.08	8.76	7	0.010	<0.001	0.02	4.86	<0.02	<0.01	0.027	<0.01	<0.01	4.93	0.05	0.004	0.12	1.01
633559	Drill Core	1.07	0.001	0.003	0.58	2.44	<2	0.004	<0.001	0.06	1.45	<0.02	0.02	0.008	<0.01	<0.01	26.19	0.05	0.001	0.11	0.33
633560	Drill Core	0.47	0.003	0.005	0.57	3.48	3	0.007	<0.001	0.03	2.38	<0.02	0.01	0.011	<0.01	<0.01	12.08	0.07	0.003	0.11	0.85
633561	Drill Core	0.51	0.002	0.004	0.68	3.34	<2	0.007	<0.001	0.03	2.28	<0.02	0.01	0.010	<0.01	<0.01	12.48	0.07	0.003	0.11	0.81
633562	Drill Core	1.33	0.002	0.007	7.62	10.45	9	0.008	<0.001	0.02	2.64	<0.02	<0.01	0.033	<0.01	<0.01	6.33	0.08	0.004	0.12	0.97
633563	Drill Core	1.56	0.001	0.005	2.60	6.33	4	0.006	<0.001	0.02	1.41	<0.02	0.01	0.022	<0.01	<0.01	10.33	0.09	0.003	0.11	0.80
633564	Drill Core	1.54	<0.001	0.007	4.18	11.32	5	0.004	<0.001	0.02	1.24	<0.02	<0.01	0.040	<0.01	<0.01	8.01	0.04	0.002	0.07	0.45
633565	Drill Core	1.08	0.003	0.006	2.15	7.02	3	0.009	<0.001	0.01	1.95	<0.02	<0.01	0.020	<0.01	<0.01	3.69	0.07	0.003	0.12	0.97
633566	Drill Core	0.81	0.003	0.002	0.10	0.61	<2	0.010	<0.001	0.02	0.70	<0.02	<0.01	0.002	<0.01	<0.01	6.99	0.09	0.004	0.16	1.24
633567	Drill Core	1.35	<0.001	0.002	1.64	1.98	<2	0.004	<0.001	0.02	0.55	<0.02	0.01	0.006	<0.01	<0.01	10.42	0.03	0.002	0.06	0.33
633568	Drill Core	1.71	<0.001	0.002	0.21	0.42	<2	0.003	<0.001	0.05	0.58	<0.02	0.03	0.001	<0.01	<0.01	30.59	0.02	<0.001	0.09	0.22
633569	Drill Core	1.41	0.003	0.007	0.53	0.48	2	0.006	<0.001	0.04	1.80	<0.02	0.02	0.001	<0.01	<0.01	23.27	0.24	0.003	0.09	0.50
633570	Rock	0.30	<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	0.02	0.13	<0.02	0.01	<0.001	<0.01	<0.01	20.60	0.03	<0.001	11.11	0.17
633571	Drill Core	1.56	0.004	0.010	0.06	0.29	<2	0.007	<0.001	0.03	0.42	<0.02	0.02	<0.001	<0.01	<0.01	15.81	0.16	0.003	0.09	0.59
633572	Drill Core	2.10	0.004	0.011	0.07	0.72	<2	0.009	<0.001	0.02	0.63	<0.02	0.01	0.002	<0.01	<0.01	10.95	0.33	0.005	0.10	0.67
633573	Drill Core	1.29	0.007	0.010	0.28	0.82	3	0.013	<0.001	<0.01	1.22	<0.02	<0.01	0.002	<0.01	<0.01	4.56	0.50	0.008	0.16	1.36
633574	Drill Core	1.65	0.007	0.019	0.07	0.23	<2	0.023	<0.001	<0.01	2.55	<0.02	<0.01	<0.001	<0.01	<0.01	3.66	0.41	0.013	0.37	3.95
633575	Drill Core	1.88	0.007	0.014	0.19	0.64	<2	0.015	<0.001	<0.01	4.21	<0.02	<0.01	0.002	<0.01	<0.01	2.69	0.27	0.007	0.23	2.14
633576	Drill Core	1.42	0.006	0.011	1.41	0.81	6	0.013	<0.001	<0.01	2.63	<0.02	<0.01	0.002	<0.01	<0.01	3.53	0.23	0.007	0.27	2.42
633577	Drill Core	1.25	0.004	0.010	0.18	0.59	<2	0.015	<0.001	<0.01	2.42	<0.02	<0.01	0.002	<0.01	<0.01	4.38	0.36	0.013	0.55	5.71
633578	Drill Core	1.23	0.004	0.012	0.14	0.51	<2	0.010	<0.001	0.01	5.57	<0.02	<0.01	0.001	<0.01	<0.01	6.67	0.35	0.005	0.13	0.91
633579	Drill Core	1.41	0.005	0.008	0.15	2.94	<2	0.012	<0.001	0.02	1.45	<0.02	0.02	0.010	<0.01	<0.01	8.61	0.26	0.007	0.24	2.09
633580	Rock Pulp	0.06	<0.001	0.661	6.12	6.68	71	<0.001	<0.001	0.09	4.46	<0.02	0.02	0.018	0.02	<0.01	1.14	0.02	0.002	0.22	3.69



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: January 11, 2011

Page: 2 of 3 **Part** 2

CERTIFICATE OF ANALYSIS

WHI10000708.1

	Method	7TD	7TD	7TD	7TD	G8SG
	Analyte	Na	K	W	S	SG
	Unit	%	%	%	%	
	MDL	0.01	0.01	0.01	0.05	0
633551	Drill Core	<0.01	1.42	<0.01	0.67	2.32
633552	Drill Core	<0.01	0.26	<0.01	3.09	2.58
633553	Drill Core	<0.01	0.04	<0.01	0.39	2.63
633554	Drill Core	<0.01	1.31	<0.01	2.19	2.27
633555	Drill Core	<0.01	0.40	<0.01	5.70	2.55
633556	Drill Core	<0.01	0.24	<0.01	6.00	2.63
633557	Drill Core	<0.01	0.17	<0.01	0.80	2.40
633558	Drill Core	<0.01	0.59	<0.01	10.87	2.63
633559	Drill Core	<0.01	0.17	<0.01	2.95	2.58
633560	Drill Core	<0.01	0.46	<0.01	4.78	2.44
633561	Drill Core	<0.01	0.44	<0.01	4.53	2.46
633562	Drill Core	<0.01	0.53	<0.01	9.63	2.71
633563	Drill Core	<0.01	0.45	<0.01	5.30	2.54
633564	Drill Core	<0.01	0.24	<0.01	7.83	2.73
633565	Drill Core	<0.01	0.53	<0.01	6.17	2.50
633566	Drill Core	<0.01	0.67	<0.01	0.94	2.30
633567	Drill Core	<0.01	0.19	<0.01	1.69	2.51
633568	Drill Core	<0.01	0.12	<0.01	0.77	2.54
633569	Drill Core	<0.01	0.25	<0.01	2.34	2.48
633570	Rock	0.05	0.05	<0.01	<0.05	2.62
633571	Drill Core	<0.01	0.29	<0.01	0.48	2.24
633572	Drill Core	<0.01	0.36	<0.01	0.87	2.23
633573	Drill Core	<0.01	0.74	<0.01	1.70	2.20
633574	Drill Core	0.01	2.54	<0.01	2.89	2.14
633575	Drill Core	<0.01	1.32	<0.01	5.37	2.38
633576	Drill Core	<0.01	1.49	<0.01	3.47	2.49
633577	Drill Core	0.01	3.80	<0.01	2.88	2.34
633578	Drill Core	<0.01	0.49	<0.01	7.27	2.45
633579	Drill Core	<0.01	1.33	<0.01	3.01	2.32
633580	Rock Pulp	2.26	1.35	<0.01	5.91	N.A.



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: January 11, 2011

Page: 3 of 3 **Part** 1

CERTIFICATE OF ANALYSIS

WHI10000708.1

	Method Analyte Unit MDL	WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD
		Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg
		kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%
		0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01
633581	Drill Core	1.52	0.001	0.008	<0.02	0.03	<2	0.011	<0.001	0.02	1.68	<0.02	0.02	<0.001	<0.01	<0.01	9.71	0.78	0.011	0.44
633582	Drill Core	0.88	<0.001	0.008	<0.02	0.07	<2	0.009	<0.001	0.01	1.23	<0.02	0.02	<0.001	<0.01	<0.01	7.15	1.19	0.010	0.40



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**

Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: January 11, 2011

Page: 3 of 3 Part 2

CERTIFICATE OF ANALYSIS

WHI10000708.1

	Method Analyte Unit MDL	7TD	7TD	7TD	7TD	G8SG
		Na	K	W	S	SG
		%	%	%	%	
		0.01	0.01	0.01	0.05	0
633581	Drill Core	0.01	2.45	<0.01	1.67	2.37
633582	Drill Core	0.02	2.87	<0.01	1.12	2.28



Acme Analytical Laboratories (Vancouver) Ltd.
1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: January 11, 2011

Page: 1 of 1 Part 1

QUALITY CONTROL REPORT

WHI10000708.1

	Method Analyte Unit MDL	WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD
		Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg	Al
		kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%	%
		0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01	0.01
Pulp Duplicates																					
633554	Drill Core	1.33	0.002	0.004	0.16	1.08	<2	0.010	<0.001	0.01	1.48	<0.02	<0.01	0.003	<0.01	<0.01	4.85	1.14	0.007	0.20	2.01
REP 633554	QC		0.002	0.004	0.16	1.10	<2	0.010	<0.001	0.01	1.46	<0.02	<0.01	0.003	<0.01	<0.01	4.96	1.12	0.006	0.19	2.02
Core Reject Duplicates																					
633579	Drill Core	1.41	0.005	0.008	0.15	2.94	<2	0.012	<0.001	0.02	1.45	<0.02	0.02	0.010	<0.01	<0.01	8.61	0.26	0.007	0.24	2.09
DUP 633579	QC		0.005	0.007	0.14	2.96	3	0.012	<0.001	0.02	1.49	<0.02	0.02	0.009	<0.01	<0.01	8.45	0.26	0.007	0.24	2.05
Reference Materials																					
STD OREAS131A	Standard		<0.001	0.031	1.70	2.88	30	0.002	0.002	0.18	5.73	<0.02	<0.01	0.008	<0.01	<0.01	5.34	0.05	0.002	3.18	4.70
STD R4T	Standard		0.061	0.496	1.50	3.39	87	0.352	0.039	0.09	24.10	<0.02	0.02	0.018	0.01	<0.01	2.17	0.04	0.017	1.43	3.97
STD SU-1B	Standard		<0.001	1.193	<0.02	0.02	7	1.985	0.065	0.07	25.38	<0.02	0.03	<0.001	<0.01	<0.01	2.25	0.06	0.028	1.82	4.47
STD R4T Expected			0.062	0.502	1.518	3.376	86	0.339	0.039	0.086	24.07	0.0087	0.0185	0.018	0.0138	0.0018	2.166	0.045	0.018	1.384	3.897
STD OREAS131A Expected			0.001	0.0322	1.72	2.83	30.9	0.0027	0.0023	0.1722	5.8166	0.0082	0.0028	0.0081	0.0047	0.001	5.286	0.0536	0.0025	3.1182	4.6057
STD SU-1B Expected			0.0004	1.185	0.0058	0.0235	6.4	1.97	0.0672	0.0703	25.54	0.00025	0.03	0.0003	0.00002	0.0003	2.21	0.06	0.032	1.79	4.39
BLK	Blank		<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	<0.01	<0.01	<0.02	<0.01	<0.001	<0.01	<0.01	<0.01	<0.01	<0.001	<0.01	<0.01
Prep Wash																					
G1	Prep Blank		<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	0.07	2.18	<0.02	0.07	<0.001	<0.01	<0.01	2.23	0.08	0.002	0.61	7.11
G1	Prep Blank		<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	0.07	2.18	<0.02	0.07	<0.001	<0.01	<0.01	2.23	0.08	0.002	0.58	7.05



Acme Analytical Laboratories (Vancouver) Ltd.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: Selwyn Resources Ltd.

Suite 700 - 509 Richards Street

Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: January 11, 2011

Page: 1 of 1 **Part** 2

QUALITY CONTROL REPORT

WHI10000708.1

	Method	7TD	7TD	7TD	7TD	G8SG
Analyte		Na	K	W	S	SG
Unit		%	%	%	%	%
MDL		0.01	0.01	0.01	0.05	0
Pulp Duplicates						
633554	Drill Core	<0.01	1.31	<0.01	2.19	2.27
REP 633554	QC	<0.01	1.31	<0.01	2.15	
Core Reject Duplicates						
633579	Drill Core	<0.01	1.33	<0.01	3.01	2.32
DUP 633579	QC	<0.01	1.30	<0.01	2.98	2.33
Reference Materials						
STD OREAS131A	Standard	0.16	3.47	<0.01	5.01	
STD R4T	Standard	0.93	1.15	<0.01	13.89	
STD SU-1B	Standard	1.72	0.61	<0.01	11.23	
STD R4T Expected		0.9	1.153	0.00016	12.9903	
STD OREAS131A Expected		0.1501	3.1584	0.0005	4.8	
STD SU-1B Expected		1.662	0.6	0.0007	8.76	
BLK	Blank	<0.01	<0.01	<0.01	<0.05	
Prep Wash						
G1	Prep Blank	2.72	3.11	<0.01	<0.05	2.69
G1	Prep Blank	2.75	3.08	<0.01	<0.05	2.70



1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: Selwyn Resources Ltd.

Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Submitted By: Jason K. Dunning

Receiving Lab: Canada-Whitehorse

Received: December 21, 2010

Report Date: January 14, 2011

Page: 1 of 3

CERTIFICATE OF ANALYSIS

WHI10000705.1

CLIENT JOB INFORMATION

Project: Selwyn Project
Shipment ID:
P.O. Number 1167
Number of Samples: 34

SAMPLE DISPOSAL

STOR-PLP Store After 90 days Invoice for Storage
STOR-RJT Store After 90 days Invoice for Storage

Acme does not accept responsibility for samples left at the laboratory after 90 days without prior written instructions for sample storage or return.

Invoice To: Selwyn Resources Ltd.
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6
Canada

CC:

SAMPLE PREPARATION AND ANALYTICAL PROCEDURES

Method Code	Number of Samples	Code Description	Test Wgt (g)	Report Status	Lab
R200-250	33	Crush split and pulverize 250g drill core to 200 mesh			WHI
7TD2	34	4 Acid digestion ICP-ES analysis.	0.5	Completed	VAN
G812	34	Specific Gravity on Pulp		Completed	VAN
7TD.1	2	4 Acid digestion ICP-ES analysis	0.1	Completed	VAN

ADDITIONAL COMMENTS



This report supersedes all previous preliminary and final reports with this file number dated prior to the date on this certificate. Signature indicates final approval; preliminary reports are unsigned and should be used for reference only.
All results are considered the confidential property of the client. Acme assumes the liabilities for actual cost of analysis only.
** asterisk indicates that an analytical result could not be provided due to unusually high levels of interference from other elements.



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: January 14, 2011

Page: 2 of 3 Part 1

CERTIFICATE OF ANALYSIS

WHI10000705.1

	Method Analyte Unit MDL	WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD
		Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg	Al
		kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%	%
		0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01	0.01
628451	Drill Core	0.31	<0.001	0.011	0.05	0.04	<2	0.002	<0.001	0.04	5.07	<0.02	0.02	<0.001	<0.01	<0.01	21.67	0.11	0.001	0.12	0.27
628452	Drill Core	0.46	0.003	0.004	1.64	1.49	4	0.009	<0.001	<0.01	1.24	<0.02	<0.01	0.004	<0.01	<0.01	1.41	0.51	0.005	0.20	1.80
628453	Drill Core	0.72	0.001	0.003	1.36	0.30	3	0.006	<0.001	<0.01	0.62	<0.02	<0.01	<0.001	<0.01	<0.01	3.38	0.72	0.005	0.13	1.20
628454	Drill Core	0.63	0.001	0.003	<0.02	0.25	<2	0.007	<0.001	0.02	0.73	<0.02	<0.01	<0.001	<0.01	<0.01	7.59	0.69	0.004	0.13	1.48
628455	Drill Core	0.42	0.002	0.006	0.88	11.22	2	0.005	<0.001	0.02	2.46	<0.02	<0.01	0.033	<0.01	<0.01	5.19	0.03	0.002	0.06	0.62
628456	Drill Core	1.26	0.002	0.008	4.45	12.79	4	0.005	<0.001	0.01	5.68	<0.02	<0.01	0.053	<0.01	<0.01	0.29	0.02	0.003	0.06	0.66
628457	Drill Core	0.92	0.003	0.007	1.07	4.92	<2	0.008	<0.001	0.02	7.43	<0.02	<0.01	0.012	<0.01	<0.01	1.69	0.04	0.003	0.08	0.84
628458	Drill Core	0.79	0.004	0.006	2.63	6.30	2	0.007	<0.001	0.02	6.70	<0.02	<0.01	0.014	<0.01	<0.01	4.02	0.06	0.003	0.09	0.99
628459	Drill Core	0.45	0.002	0.002	0.18	1.80	<2	0.005	<0.001	0.03	1.31	<0.02	0.01	0.005	<0.01	<0.01	17.19	0.06	0.002	0.11	0.79
628460	Drill Core	0.44	0.002	0.001	0.17	1.33	<2	0.003	<0.001	0.02	0.71	<0.02	<0.01	0.004	<0.01	<0.01	10.39	0.04	0.002	0.05	0.40
628461	Drill Core	0.45	0.002	0.001	0.17	1.11	<2	0.003	<0.001	0.02	0.55	<0.02	<0.01	0.003	<0.01	<0.01	9.24	0.05	0.002	0.05	0.38
628462	Drill Core	0.61	0.002	0.003	0.13	1.16	<2	0.005	<0.001	0.01	1.22	<0.02	<0.01	0.003	<0.01	<0.01	6.42	0.12	0.002	0.06	0.67
628463	Drill Core	0.73	0.008	0.004	0.05	0.84	<2	0.012	<0.001	<0.01	1.54	<0.02	<0.01	0.002	<0.01	<0.01	3.95	0.05	0.004	0.14	1.81
628464	Drill Core	0.21	0.006	0.012	6.20	9.81	2	0.010	<0.001	0.03	6.53	<0.02	<0.01	0.027	<0.01	<0.01	3.25	0.04	0.003	0.09	1.15
628465	Drill Core	0.69	<0.001	0.002	0.28	1.57	<2	0.002	<0.001	0.07	1.48	<0.02	0.02	0.005	<0.01	<0.01	30.71	0.03	<0.001	0.11	0.15
628466	Drill Core	0.44	0.001	0.003	2.29	6.27	<2	0.004	<0.001	0.03	1.41	<0.02	<0.01	0.018	<0.01	<0.01	13.57	0.05	0.002	0.09	0.55
628467	Drill Core	0.72	<0.001	0.003	>10	20.76	3	0.001	<0.001	0.02	0.83	<0.02	<0.01	0.109	0.01	<0.01	8.31	0.03	<0.001	0.02	0.12
628468	Drill Core	0.46	<0.001	0.002	>10	18.38	3	<0.001	<0.001	0.02	0.24	<0.02	<0.01	0.098	<0.01	<0.01	16.35	0.01	<0.001	0.03	0.06
628469	Drill Core	0.66	0.001	0.002	0.34	0.17	<2	0.003	<0.001	0.03	1.89	<0.02	0.01	<0.001	<0.01	<0.01	22.71	0.05	0.002	0.11	0.66
628470	Rock	0.33	<0.001	<0.001	0.03	0.03	<2	<0.001	<0.001	0.02	0.15	<0.02	0.01	<0.001	<0.01	<0.01	21.13	0.02	<0.001	11.34	0.13
628471	Drill Core	0.97	0.002	0.005	0.12	0.16	<2	0.006	<0.001	0.03	3.28	<0.02	0.01	<0.001	<0.01	<0.01	17.95	0.06	0.002	0.13	0.88
628472	Drill Core	1.15	0.002	0.003	0.15	0.52	<2	0.006	<0.001	0.03	1.03	<0.02	0.01	0.001	<0.01	<0.01	18.87	0.05	0.002	0.11	0.65
628473	Drill Core	0.50	0.001	0.003	0.12	0.97	<2	0.005	<0.001	0.01	0.80	<0.02	<0.01	0.002	<0.01	<0.01	6.10	0.03	0.002	0.07	0.48
628474	Drill Core	0.84	0.002	0.007	0.46	1.49	<2	0.006	<0.001	0.04	0.91	<0.02	0.01	0.003	<0.01	<0.01	18.19	0.17	0.003	0.13	0.69
628475	Drill Core	1.25	0.001	0.003	0.09	0.14	<2	0.003	<0.001	0.05	0.79	<0.02	0.02	<0.001	<0.01	<0.01	28.70	0.11	0.001	0.13	0.19
628476	Drill Core	1.10	0.004	0.013	0.21	0.94	<2	0.007	<0.001	0.03	1.62	<0.02	0.01	0.003	<0.01	<0.01	17.51	0.87	0.003	0.09	0.56
628477	Drill Core	1.15	0.007	0.016	0.29	1.57	3	0.012	<0.001	0.02	1.01	<0.02	<0.01	0.004	<0.01	<0.01	10.28	0.76	0.006	0.14	1.01
628478	Drill Core	0.83	0.002	0.004	0.13	0.58	<2	0.004	<0.001	0.02	0.61	<0.02	<0.01	0.001	<0.01	<0.01	13.83	0.28	0.003	0.07	0.34
628479	Drill Core	1.02	0.005	0.009	0.33	2.53	2	0.009	<0.001	0.01	1.44	<0.02	<0.01	0.006	<0.01	<0.01	9.85	0.34	0.005	0.11	0.84
628480	Rock Pulp	0.06	<0.001	0.680	6.36	6.77	71	<0.001	<0.001	0.10	4.64	<0.02	0.02	0.018	0.03	<0.01	1.34	0.02	0.002	0.24	4.95



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: January 14, 2011

Page: 2 of 3 **Part** 2

CERTIFICATE OF ANALYSIS

WHI10000705.1

	Method Analyte Unit MDL	7TD	7TD	7TD	7TD	G8SG	7TD.1
		Na	K	W	S	SG	Pb
		%	%	%	%		%
		0.01	0.01	0.01	0.05	0	0.02
628451	Drill Core	0.01	0.15	<0.01	6.73	2.61	
628452	Drill Core	<0.01	0.99	<0.01	2.38	2.34	
628453	Drill Core	<0.01	0.70	<0.01	1.01	2.41	
628454	Drill Core	<0.01	0.98	<0.01	0.96	2.50	
628455	Drill Core	<0.01	0.40	<0.01	9.11	2.60	
628456	Drill Core	<0.01	0.38	<0.01	14.11	2.70	
628457	Drill Core	<0.01	0.48	<0.01	12.04	2.50	
628458	Drill Core	<0.01	0.59	<0.01	12.22	2.57	
628459	Drill Core	<0.01	0.43	<0.01	2.58	2.33	
628460	Drill Core	<0.01	0.21	<0.01	1.46	2.44	
628461	Drill Core	<0.01	0.21	<0.01	1.19	2.43	
628462	Drill Core	<0.01	0.39	<0.01	2.00	2.38	
628463	Drill Core	<0.01	1.03	<0.01	2.25	2.09	
628464	Drill Core	<0.01	0.66	<0.01	13.93	2.64	
628465	Drill Core	<0.01	0.08	<0.01	2.67	2.58	
628466	Drill Core	<0.01	0.27	<0.01	5.48	2.55	
628467	Drill Core	<0.01	0.06	<0.01	13.49	3.17	12.57
628468	Drill Core	<0.01	0.03	<0.01	11.37	3.13	11.34
628469	Drill Core	<0.01	0.32	<0.01	2.46	2.41	
628470	Rock	0.01	0.03	<0.01	<0.05	2.59	
628471	Drill Core	<0.01	0.46	<0.01	4.17	2.41	
628472	Drill Core	<0.01	0.34	<0.01	1.54	2.32	
628473	Drill Core	<0.01	0.27	<0.01	1.36	2.43	
628474	Drill Core	<0.01	0.35	<0.01	1.94	2.27	
628475	Drill Core	<0.01	0.10	<0.01	1.05	2.44	
628476	Drill Core	<0.01	0.29	<0.01	2.48	2.31	
628477	Drill Core	<0.01	0.54	<0.01	2.02	2.11	
628478	Drill Core	<0.01	0.19	<0.01	1.06	2.34	
628479	Drill Core	<0.01	0.47	<0.01	3.03	2.23	
628480	Rock Pulp	2.32	1.33	<0.01	5.99	N.A.	



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: January 14, 2011

Page: 3 of 3 **Part** 1

CERTIFICATE OF ANALYSIS

WHI10000705.1

	Method	WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD
	Analyte	Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg
	Unit	kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%
	MDL	0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01
628481	Drill Core	0.60	0.009	0.015	0.06	1.26	<2	0.014	<0.001	0.01	1.86	<0.02	<0.01	0.004	<0.01	<0.01	5.29	0.09	0.005	0.16
628482	Drill Core	0.75	0.005	0.012	0.18	0.98	2	0.021	<0.001	<0.01	1.52	<0.02	<0.01	0.003	<0.01	<0.01	8.20	1.93	0.014	0.20
628483	Drill Core	1.07	0.002	0.003	0.03	<0.01	<2	0.004	<0.001	0.04	1.94	<0.02	0.02	<0.001	<0.01	<0.01	25.90	0.04	0.002	0.35
628484	Drill Core	0.78	0.004	0.008	0.04	0.07	<2	0.012	0.001	0.02	5.72	<0.02	0.03	<0.001	<0.01	<0.01	20.82	5.35	0.005	0.22



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: January 14, 2011

Page: 3 of 3 **Part** 2

CERTIFICATE OF ANALYSIS

WHI10000705.1

	Method	7TD	7TD	7TD	7TD	G8SG	7TD.1
	Analyte	Na	K	W	S	SG	Pb
	Unit	%	%	%	%		%
	MDL	0.01	0.01	0.01	0.05	0	0.02
628481	Drill Core	0.01	0.66	<0.01	2.95	2.14	
628482	Drill Core	<0.01	1.08	<0.01	2.42	1.92	
628483	Drill Core	<0.01	1.32	<0.01	2.21	2.46	
628484	Drill Core	0.02	1.31	<0.01	6.67	2.49	



Acme Analytical Laboratories (Vancouver) Ltd.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: **Selwyn Resources Ltd.**

Suite 700 - 509 Richards Street

Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: January 14, 2011

Page: 1 of 2 Part 1

QUALITY CONTROL REPORT

WHI10000705.1

	Method Analyte Unit MDL	WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD
		Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg	Al
		kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%	%
		0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01	0.01
Pulp Duplicates																					
628465	Drill Core	0.69	<0.001	0.002	0.28	1.57	<2	0.002	<0.001	0.07	1.48	<0.02	0.02	0.005	<0.01	<0.01	30.71	0.03	<0.001	0.11	0.15
REP 628465	QC		<0.001	0.002	0.28	1.55	<2	0.002	<0.001	0.07	1.46	<0.02	0.02	0.005	<0.01	<0.01	30.10	0.03	<0.001	0.11	0.15
628468	Drill Core	0.46	<0.001	0.002	>10	18.38	3	<0.001	<0.001	0.02	0.24	<0.02	<0.01	0.098	<0.01	<0.01	16.35	0.01	<0.001	0.03	0.06
REP 628468	QC																				
628483	Drill Core	1.07	0.002	0.003	0.03	<0.01	<2	0.004	<0.001	0.04	1.94	<0.02	0.02	<0.001	<0.01	<0.01	25.90	0.04	0.002	0.35	2.46
REP 628483	QC		0.001	0.003	0.02	<0.01	<2	0.004	<0.001	0.04	1.95	<0.02	0.02	<0.001	<0.01	<0.01	25.49	0.05	0.002	0.35	2.42
Core Reject Duplicates																					
628463	Drill Core	0.73	0.008	0.004	0.05	0.84	<2	0.012	<0.001	<0.01	1.54	<0.02	<0.01	0.002	<0.01	<0.01	3.95	0.05	0.004	0.14	1.81
DUP 628463	QC		0.008	0.004	0.06	0.90	<2	0.012	<0.001	<0.01	1.64	<0.02	<0.01	0.003	<0.01	<0.01	3.65	0.05	0.004	0.13	1.80
Reference Materials																					
STD CCU-1C	Standard																				
STD CZN-3	Standard																				
STD OREAS131A	Standard		<0.001	0.032	1.72	2.91	31	0.002	0.002	0.18	5.72	<0.02	<0.01	0.008	<0.01	<0.01	5.19	0.05	0.002	3.16	4.56
STD OREAS131A	Standard		0.001	0.032	1.71	2.85	31	0.003	0.002	0.17	5.86	<0.02	<0.01	0.008	<0.01	<0.01	5.37	0.06	0.002	3.11	4.58
STD PTC-1A	Standard																				
STD R4T	Standard		0.063	0.509	1.55	3.47	86	0.354	0.040	0.09	24.25	<0.02	0.02	0.018	0.02	<0.01	2.20	0.05	0.018	1.42	3.95
STD R4T	Standard		0.069	0.514	1.59	3.42	91	0.357	0.043	0.09	24.45	<0.02	0.02	0.019	0.02	<0.01	2.19	0.06	0.018	1.43	3.95
STD SARM 71	Standard																				
STD SU-1B	Standard		<0.001	1.200	<0.02	0.02	6	1.996	0.067	0.07	25.70	<0.02	0.03	<0.001	<0.01	<0.01	2.26	0.06	0.030	1.81	4.46
STD SU-1B	Standard		0.002	1.181	<0.02	0.03	7	1.997	0.069	0.07	25.67	<0.02	0.03	<0.001	<0.01	<0.01	2.24	0.07	0.033	1.80	4.36
STD CZN-3 Expected																					
STD CCU-1C Expected																					
STD PTC-1A Expected																					
STD R4T Expected			0.062	0.502	1.518	3.376	86	0.339	0.039	0.086	24.07	0.0087	0.0185	0.018	0.0138	0.0018	2.166	0.045	0.018	1.384	3.897
STD OREAS131A Expected			0.001	0.0322	1.72	2.83	30.9	0.0027	0.0023	0.1722	5.8166	0.0082	0.0028	0.0081	0.0047	0.001	5.286	0.0536	0.0025	3.1182	4.6057
STD SU-1B Expected			0.0004	1.185	0.0058	0.0235	6.4	1.97	0.0672	0.0703	25.54	0.00025	0.03	0.0003	0.00002	0.0003	2.21	0.06	0.032	1.79	4.39
BLK	Blank		<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	<0.01	<0.01	<0.02	<0.01	<0.001	<0.01	<0.01	<0.01	<0.01	<0.001	<0.01	<0.01
BLK	Blank																				



Acme Analytical Laboratories (Vancouver) Ltd.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: Selwyn Resources Ltd.

Suite 700 - 509 Richards Street

Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: January 14, 2011

Page: 1 of 2 **Part** 2

QUALITY CONTROL REPORT

WHI10000705.1

Method		7TD	7TD	7TD	7TD	G8SG	7TD.1
Analyte		Na	K	W	S	SG	Pb
Unit		%	%	%	%		%
MDL		0.01	0.01	0.01	0.05	0	0.02
Pulp Duplicates							
628465	Drill Core	<0.01	0.08	<0.01	2.67	2.58	
REP 628465	QC	<0.01	0.08	<0.01	2.62		
628468	Drill Core	<0.01	0.03	<0.01	11.37	3.13	11.34
REP 628468	QC						10.81
628483	Drill Core	<0.01	1.32	<0.01	2.21	2.46	
REP 628483	QC	<0.01	1.39	<0.01	2.19		
Core Reject Duplicates							
628463	Drill Core	<0.01	1.03	<0.01	2.25	2.09	
DUP 628463	QC	<0.01	1.02	<0.01	2.38	2.09	
Reference Materials							
STD CCU-1C	Standard						0.37
STD CZN-3	Standard						0.12
STD OREAS131A	Standard	0.16	3.41	<0.01	5.03		
STD OREAS131A	Standard	0.15	3.36	<0.01	4.74		
STD PTC-1A	Standard						0.05
STD R4T	Standard	0.93	1.15	<0.01	14.18		
STD R4T	Standard	0.94	1.20	<0.01	12.10		
STD SARM 71	Standard						<0.02
STD SU-1B	Standard	1.69	0.61	<0.01	11.48		
STD SU-1B	Standard	1.71	0.63	<0.01	8.08		
STD CZN-3 Expected							0.113
STD CCU-1C Expected							0.34
STD PTC-1A Expected							0.05
STD R4T Expected		0.9	1.153	0.00016	12.9903		
STD OREAS131A Expected		0.1501	3.1584	0.0005	4.8		
STD SU-1B Expected		1.662	0.6	0.0007	8.76		
BLK	Blank	<0.01	<0.01	<0.01	<0.05		
BLK	Blank						<0.02



Acme Analytical Laboratories (Vancouver) Ltd.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: **Selwyn Resources Ltd.**

Suite 700 - 509 Richards Street

Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: January 14, 2011

Page: 2 of 2 Part 1

QUALITY CONTROL REPORT

WHI10000705.1

		WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD
		Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg
		kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%
		0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01
BLK	Blank		<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	<0.01	<0.01	<0.02	<0.01	<0.001	<0.01	<0.01	<0.01	<0.01	<0.001	<0.01
Prep Wash																				
G1	Prep Blank		<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	0.07	2.11	<0.02	0.07	<0.001	<0.01	<0.01	2.29	0.07	0.002	0.57
G1	Prep Blank		<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	0.07	2.11	<0.02	0.08	<0.001	<0.01	<0.01	2.28	0.07	0.001	0.55



Acme Analytical Laboratories (Vancouver) Ltd.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: **Selwyn Resources Ltd.**

Suite 700 - 509 Richards Street

Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: January 14, 2011

Page: 2 of 2 **Part** 2

QUALITY CONTROL REPORT

WHI10000705.1

		7TD	7TD	7TD	7TD	G8SG	7TD.1
		Na	K	W	S	SG	Pb
		%	%	%	%		%
		0.01	0.01	0.01	0.05	0	0.02
BLK	Blank	<0.01	<0.01	<0.01	<0.05		
Prep Wash							
G1	Prep Blank	2.77	3.14	<0.01	<0.05	2.69	
G1	Prep Blank	2.79	3.09	<0.01	<0.05	2.66	



1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: Selwyn Resources Ltd.

Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Submitted By: Jason K. Dunning

Receiving Lab: Canada-Whitehorse

Received: December 20, 2010

Report Date: January 11, 2011

Page: 1 of 3

CERTIFICATE OF ANALYSIS

WHI10000704.1

CLIENT JOB INFORMATION

Project: Selwyn Project
Shipment ID:
P.O. Number 1167
Number of Samples: 31

SAMPLE DISPOSAL

STOR-PLP Store After 90 days Invoice for Storage
STOR-RJT Store After 90 days Invoice for Storage

Acme does not accept responsibility for samples left at the laboratory after 90 days without prior written instructions for sample storage or return.

Invoice To: Selwyn Resources Ltd.
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6
Canada

CC:

SAMPLE PREPARATION AND ANALYTICAL PROCEDURES

Method Code	Number of Samples	Code Description	Test Wgt (g)	Report Status	Lab
R200-250	30	Crush split and pulverize 250g drill core to 200 mesh			WHI
7TD2	31	4 Acid digestion ICP-ES analysis.	0.5	Completed	VAN
G812	31	Specific Gravity on Pulp		Completed	VAN
7TD.1	3	4 Acid digestion ICP-ES analysis	0.1	Completed	VAN

ADDITIONAL COMMENTS



This report supersedes all previous preliminary and final reports with this file number dated prior to the date on this certificate. Signature indicates final approval; preliminary reports are unsigned and should be used for reference only.
All results are considered the confidential property of the client. Acme assumes the liabilities for actual cost of analysis only.
** asterisk indicates that an analytical result could not be provided due to unusually high levels of interference from other elements.



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**

Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: January 11, 2011

Page: 2 of 3 Part 1

CERTIFICATE OF ANALYSIS

WHI10000704.1

	Method Analyte Unit MDL	WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD
		Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg	Al
		kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%	%
		0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01	0.01
632451	Drill Core	1.90	0.001	0.001	0.02	<0.01	<2	0.002	<0.001	0.04	1.59	<0.02	0.01	<0.001	<0.01	<0.01	23.91	0.06	0.001	0.15	0.85
632452	Drill Core	0.66	<0.001	0.003	<0.02	0.02	<2	0.005	<0.001	<0.01	0.79	<0.02	<0.01	<0.001	<0.01	<0.01	2.34	0.34	0.002	0.15	1.04
632453	Drill Core	0.58	<0.001	0.002	<0.02	<0.01	<2	<0.001	<0.001	0.06	1.38	<0.02	0.02	<0.001	<0.01	<0.01	33.62	0.02	<0.001	0.16	0.11
632454	Drill Core	1.11	0.001	0.004	0.08	0.33	<2	0.006	<0.001	0.01	1.00	<0.02	<0.01	0.001	<0.01	<0.01	6.31	0.31	0.002	0.17	1.15
632455	Drill Core	0.66	0.001	0.004	1.53	2.55	<2	0.005	<0.001	0.02	1.17	<0.02	0.01	0.008	<0.01	<0.01	9.68	0.05	<0.001	0.28	0.73
632456	Drill Core	1.22	<0.001	0.012	0.16	0.05	<2	0.004	<0.001	0.03	15.29	<0.02	0.01	<0.001	<0.01	<0.01	15.94	0.05	0.002	0.09	0.43
632457	Drill Core	0.75	0.002	0.006	0.07	0.50	<2	0.005	<0.001	0.03	0.99	<0.02	0.01	0.002	<0.01	<0.01	15.89	0.19	0.002	0.12	0.50
632458	Drill Core	1.52	<0.001	<0.001	0.14	0.11	<2	0.003	<0.001	0.03	0.63	<0.02	0.01	<0.001	<0.01	<0.01	21.22	0.03	<0.001	0.08	0.39
632459	Drill Core	1.22	0.002	0.009	2.24	16.54	3	0.006	<0.001	0.03	3.10	<0.02	<0.01	0.035	0.01	<0.01	7.02	0.05	0.002	0.15	0.61
632460	Drill Core	0.90	<0.001	0.002	1.77	4.42	<2	0.003	<0.001	0.04	1.62	<0.02	0.02	0.016	<0.01	<0.01	20.97	0.05	<0.001	0.13	0.33
632461	Drill Core	0.86	<0.001	0.003	2.43	4.81	<2	0.003	<0.001	0.04	1.61	<0.02	0.02	0.016	<0.01	<0.01	20.37	0.07	<0.001	0.12	0.36
632462	Drill Core	0.89	<0.001	0.002	0.22	0.38	<2	0.003	<0.001	0.05	0.69	<0.02	0.02	0.001	<0.01	<0.01	28.82	0.04	<0.001	0.22	0.54
632463	Drill Core	1.12	<0.001	0.002	4.40	5.36	3	0.003	<0.001	0.03	2.18	<0.02	<0.01	0.019	<0.01	<0.01	12.50	0.05	0.002	0.08	0.41
632464	Drill Core	1.67	0.001	0.003	5.41	12.72	4	0.003	<0.001	0.04	2.28	<0.02	0.01	0.042	<0.01	<0.01	15.97	0.03	<0.001	0.07	0.30
632465	Drill Core	1.76	0.002	0.003	2.74	5.70	<2	0.006	<0.001	0.02	2.38	<0.02	<0.01	0.016	<0.01	<0.01	6.59	0.06	0.002	0.10	0.73
632466	Drill Core	1.43	0.001	0.004	2.38	12.30	3	0.004	<0.001	0.03	1.49	<0.02	0.01	0.031	<0.01	<0.01	19.37	0.03	0.001	0.08	0.43
632467	Drill Core	1.09	<0.001	0.003	6.63	14.34	3	0.002	<0.001	0.03	0.82	<0.02	<0.01	0.054	<0.01	<0.01	14.24	0.03	<0.001	0.04	0.18
632468	Drill Core	2.23	0.001	0.002	0.36	3.09	<2	0.004	<0.001	0.04	0.93	<0.02	0.02	0.009	<0.01	<0.01	29.77	0.04	0.001	0.11	0.56
632469	Drill Core	2.03	<0.001	0.001	0.73	2.51	<2	0.002	<0.001	0.05	0.80	<0.02	0.02	0.008	<0.01	<0.01	29.61	0.04	<0.001	0.09	0.20
632470	Rock	0.36	<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	0.02	0.18	<0.02	0.01	<0.001	<0.01	<0.01	22.11	0.03	<0.001	11.30	0.16
632471	Drill Core	2.37	<0.001	0.002	0.76	2.23	<2	0.004	<0.001	0.02	0.97	<0.02	0.01	0.009	<0.01	<0.01	12.21	0.05	0.002	0.11	0.65
632472	Drill Core	1.54	<0.001	0.001	0.42	1.32	<2	0.003	<0.001	0.03	0.81	<0.02	0.01	0.006	<0.01	<0.01	20.78	0.04	0.001	0.11	0.55
632473	Drill Core	1.32	<0.001	0.003	6.39	13.53	3	<0.001	<0.001	0.05	1.01	<0.02	0.01	0.056	<0.01	<0.01	25.08	0.01	<0.001	0.08	0.04
632474	Drill Core	3.55	<0.001	0.006	>10	28.03	5	<0.001	<0.001	0.02	0.17	<0.02	<0.01	0.127	<0.01	<0.01	15.22	0.02	<0.001	0.03	0.02
632475	Drill Core	1.73	<0.001	0.003	>10	20.59	5	<0.001	<0.001	0.02	0.61	<0.02	<0.01	0.104	<0.01	<0.01	12.32	0.02	<0.001	0.03	0.06
632476	Drill Core	1.68	<0.001	0.004	>10	19.20	8	0.001	<0.001	0.02	1.00	<0.02	<0.01	0.089	<0.01	<0.01	8.42	0.01	<0.001	0.02	0.10
632477	Drill Core	1.22	0.001	0.003	2.89	3.15	3	0.005	<0.001	0.04	1.75	<0.02	0.01	0.015	<0.01	<0.01	21.66	0.06	0.002	0.14	0.82
632478	Drill Core	1.86	0.001	0.003	0.33	0.36	<2	0.006	<0.001	0.02	1.11	<0.02	<0.01	0.002	<0.01	<0.01	7.61	0.07	0.003	0.10	0.75
632479	Drill Core	0.91	0.004	0.005	0.03	0.17	<2	0.012	<0.001	0.02	1.85	<0.02	0.01	0.001	<0.01	<0.01	10.84	0.08	0.007	0.29	2.64
632480	Rock Pulp	0.05	<0.001	0.658	5.92	6.97	70	<0.001	0.001	0.10	4.83	<0.02	0.02	0.018	0.04	<0.01	1.37	0.02	<0.001	0.25	5.11



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: January 11, 2011

Page: 2 of 3 **Part** 2

CERTIFICATE OF ANALYSIS

WHI10000704.1

	Method Analyte Unit MDL	7TD	7TD	7TD	7TD	G8SG	7TD.1
		Na	K	W	S	SG	Pb
		%	%	%	%		%
		0.01	0.01	0.01	0.05	0	0.02
632451	Drill Core	<0.01	0.46	<0.01	1.83	2.42	
632452	Drill Core	<0.01	0.53	<0.01	0.73	2.34	
632453	Drill Core	<0.01	0.05	<0.01	1.61	2.56	
632454	Drill Core	<0.01	0.54	<0.01	1.11	2.37	
632455	Drill Core	<0.01	0.19	<0.01	2.76	2.44	
632456	Drill Core	<0.01	0.22	<0.01	17.81	2.82	
632457	Drill Core	<0.01	0.24	<0.01	1.26	2.38	
632458	Drill Core	<0.01	0.18	<0.01	0.70	2.43	
632459	Drill Core	<0.01	0.25	<0.01	11.39	2.67	
632460	Drill Core	<0.01	0.13	<0.01	4.20	2.60	
632461	Drill Core	<0.01	0.15	<0.01	4.48	2.58	
632462	Drill Core	<0.01	0.21	<0.01	0.98	2.40	
632463	Drill Core	<0.01	0.20	<0.01	5.53	2.60	
632464	Drill Core	<0.01	0.14	<0.01	9.48	2.78	
632465	Drill Core	<0.01	0.38	<0.01	5.70	2.57	
632466	Drill Core	<0.01	0.21	<0.01	7.91	2.71	
632467	Drill Core	<0.01	0.09	<0.01	8.70	2.87	
632468	Drill Core	<0.01	0.27	<0.01	2.59	2.45	
632469	Drill Core	<0.01	0.10	<0.01	2.19	2.58	
632470	Rock	0.02	0.03	<0.01	<0.05	2.60	
632471	Drill Core	<0.01	0.33	<0.01	2.17	2.44	
632472	Drill Core	<0.01	0.28	<0.01	1.53	2.48	
632473	Drill Core	<0.01	0.01	<0.01	8.43	2.89	
632474	Drill Core	<0.01	<0.01	<0.01	15.59	3.22	13.36
632475	Drill Core	<0.01	0.02	<0.01	12.27	3.17	13.18
632476	Drill Core	<0.01	0.05	<0.01	11.86	3.09	12.79
632477	Drill Core	<0.01	0.48	<0.01	3.92	2.60	
632478	Drill Core	<0.01	0.43	<0.01	1.25	2.44	
632479	Drill Core	<0.01	1.89	<0.01	2.04	2.23	
632480	Rock Pulp	2.22	1.35	<0.01	5.02	N.A.	



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: January 11, 2011

Page: 3 of 3 **Part** 1

CERTIFICATE OF ANALYSIS

WHI10000704.1

	Method	WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD
	Analyte	Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg	Al
	Unit	kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%	%
	MDL	0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01	0.01
632481	Drill Core	1.35	0.004	0.005	<0.02	0.10	<2	0.014	<0.001	0.02	2.57	<0.02	<0.01	<0.001	<0.01	<0.01	8.60	0.06	0.006	0.29	2.97



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: January 11, 2011

Page: 3 of 3 **Part** 2

CERTIFICATE OF ANALYSIS

WHI10000704.1

	Method	7TD	7TD	7TD	7TD	G8SG	7TD.1
	Analyte	Na	K	W	S	SG	Pb
	Unit	%	%	%	%		%
	MDL	0.01	0.01	0.01	0.05	0	0.02
632481	Drill Core	<0.01	2.27	<0.01	2.80	2.28	



Acme Analytical Laboratories (Vancouver) Ltd.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: Selwyn Resources Ltd.

Suite 700 - 509 Richards Street

Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: January 11, 2011

Page: 1 of 1 Part 1

QUALITY CONTROL REPORT

WHI10000704.1

	Method Analyte Unit MDL	WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD
		Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg	Al
		kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%	%
		0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01	0.01
Pulp Duplicates																					
632456	Drill Core	1.22	<0.001	0.012	0.16	0.05	<2	0.004	<0.001	0.03	15.29	<0.02	0.01	<0.001	<0.01	<0.01	15.94	0.05	0.002	0.09	0.43
REP 632456	QC		<0.001	0.012	0.16	0.05	<2	0.004	<0.001	0.03	15.76	<0.02	0.01	<0.001	<0.01	<0.01	16.23	0.05	0.001	0.09	0.43
632476	Drill Core	1.68	<0.001	0.004	>10	19.20	8	0.001	<0.001	0.02	1.00	<0.02	<0.01	0.089	<0.01	<0.01	8.42	0.01	<0.001	0.02	0.10
REP 632476	QC																				
Core Reject Duplicates																					
632472	Drill Core	1.54	<0.001	0.001	0.42	1.32	<2	0.003	<0.001	0.03	0.81	<0.02	0.01	0.006	<0.01	<0.01	20.78	0.04	0.001	0.11	0.55
DUP 632472	QC		<0.001	0.001	0.45	1.43	<2	0.003	<0.001	0.03	0.85	<0.02	0.01	0.006	<0.01	<0.01	21.00	0.04	<0.001	0.10	0.57
Reference Materials																					
STD CCU-1C	Standard																				
STD CZN-3	Standard																				
STD OREAS131A	Standard		<0.001	0.032	1.69	2.87	31	0.003	0.002	0.17	5.86	<0.02	<0.01	0.008	<0.01	<0.01	5.44	0.05	0.002	3.11	4.57
STD PTC-1A	Standard																				
STD R4T	Standard		0.065	0.518	1.57	3.49	89	0.355	0.041	0.09	24.80	<0.02	0.02	0.019	0.02	<0.01	2.22	0.05	0.019	1.43	3.98
STD SARM 71	Standard																				
STD SU-1B	Standard		<0.001	1.164	<0.02	0.03	7	1.956	0.067	0.07	25.53	<0.02	0.03	<0.001	<0.01	<0.01	2.20	0.07	0.031	1.77	4.30
STD R4T Expected			0.062	0.502	1.518	3.376	86	0.339	0.039	0.086	24.07	0.0087	0.0185	0.018	0.0138	0.0018	2.166	0.045	0.018	1.384	3.897
STD OREAS131A Expected			0.001	0.0322	1.72	2.83	30.9	0.0027	0.0023	0.1722	5.8166	0.0082	0.0028	0.0081	0.0047	0.001	5.286	0.0536	0.0025	3.1182	4.6057
STD SU-1B Expected			0.0004	1.185	0.0058	0.0235	6.4	1.97	0.0672	0.0703	25.54	0.00025	0.03	0.0003	0.00002	0.0003	2.21	0.06	0.032	1.79	4.39
STD CZN-3 Expected																					
STD CCU-1C Expected																					
STD PTC-1A Expected																					
BLK	Blank		<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	<0.01	<0.01	<0.02	<0.01	<0.001	<0.01	<0.01	<0.01	<0.01	<0.001	<0.01	<0.01
BLK	Blank																				
Prep Wash																					
G1	Prep Blank		<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	0.07	2.36	<0.02	0.07	<0.001	<0.01	<0.01	2.39	0.08	0.001	0.63	7.97
G1	Prep Blank		<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	0.08	2.41	<0.02	0.08	<0.001	<0.01	<0.01	2.41	0.08	<0.001	0.65	8.06



Acme Analytical Laboratories (Vancouver) Ltd.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: Selwyn Resources Ltd.

Suite 700 - 509 Richards Street

Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: January 11, 2011

Page: 1 of 1 **Part** 2

QUALITY CONTROL REPORT

WHI10000704.1

		Method	7TD	7TD	7TD	7TD	G8SG	7TD.1
		Analyte	Na	K	W	S	SG	Pb
		Unit	%	%	%	%		%
		MDL	0.01	0.01	0.01	0.05	0	0.02
Pulp Duplicates								
632456	Drill Core		<0.01	0.22	<0.01	17.81	2.82	
REP 632456	QC		<0.01	0.23	<0.01	18.17		
632476	Drill Core		<0.01	0.05	<0.01	11.86	3.09	12.79
REP 632476	QC							12.82
Core Reject Duplicates								
632472	Drill Core		<0.01	0.28	<0.01	1.53	2.48	
DUP 632472	QC		<0.01	0.28	<0.01	1.59	2.46	
Reference Materials								
STD CCU-1C	Standard							0.41
STD CZN-3	Standard							0.14
STD OREAS131A	Standard		0.15	3.44	<0.01	4.72		
STD PTC-1A	Standard							0.09
STD R4T	Standard		0.94	1.20	<0.01	11.97		
STD SARM 71	Standard							0.04
STD SU-1B	Standard		1.70	0.62	<0.01	8.05		
STD R4T Expected			0.9	1.153	0.00016	12.9903		
STD OREAS131A Expected			0.1501	3.1584	0.0005	4.8		
STD SU-1B Expected			1.662	0.6	0.0007	8.76		
STD CZN-3 Expected								0.113
STD CCU-1C Expected								0.34
STD PTC-1A Expected								0.05
BLK	Blank		<0.01	<0.01	<0.01	<0.05		
BLK	Blank							<0.02
Prep Wash								
G1	Prep Blank		2.72	2.97	<0.01	<0.05	2.73	
G1	Prep Blank		2.72	3.05	<0.01	<0.05	2.65	



1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: Selwyn Resources Ltd.

Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Submitted By: Jason K. Dunning

Receiving Lab: Canada-Whitehorse

Received: December 20, 2010

Report Date: January 10, 2011

Page: 1 of 2

CERTIFICATE OF ANALYSIS

WHI10000703.1

CLIENT JOB INFORMATION

Project: Selwyn Project
Shipment ID:
P.O. Number 1167
Number of Samples: 23

SAMPLE DISPOSAL

STOR-PLP Store After 90 days Invoice for Storage
STOR-RJT Store After 90 days Invoice for Storage

Acme does not accept responsibility for samples left at the laboratory after 90 days without prior written instructions for sample storage or return.

Invoice To: Selwyn Resources Ltd.
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6
Canada

CC:

SAMPLE PREPARATION AND ANALYTICAL PROCEDURES

Method Code	Number of Samples	Code Description	Test Wgt (g)	Report Status	Lab
R200-250	22	Crush split and pulverize 250g drill core to 200 mesh			WHI
7TD2	23	4 Acid digestion ICP-ES analysis.	0.5	Completed	VAN
G812	23	Specific Gravity on Pulp		Completed	VAN

ADDITIONAL COMMENTS



This report supersedes all previous preliminary and final reports with this file number dated prior to the date on this certificate. Signature indicates final approval; preliminary reports are unsigned and should be used for reference only.
All results are considered the confidential property of the client. Acme assumes the liabilities for actual cost of analysis only.
** asterisk indicates that an analytical result could not be provided due to unusually high levels of interference from other elements.



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: January 10, 2011

Page: 2 of 2 Part 1

CERTIFICATE OF ANALYSIS

WHI10000703.1

	Method Analyte Unit MDL	WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD
		Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg	Al
		kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%	%
		0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01	0.01
633601	Drill Core	1.43	<0.001	0.007	0.51	3.77	2	0.006	<0.001	0.03	2.06	<0.02	0.02	0.014	<0.01	<0.01	17.22	0.70	0.003	0.28	1.21
633602	Drill Core	0.63	<0.001	0.005	0.20	0.19	<2	0.012	<0.001	0.01	1.68	<0.02	0.01	0.001	<0.01	<0.01	9.13	2.04	0.007	0.56	3.12
633603	Drill Core	0.83	<0.001	0.005	0.06	0.80	<2	0.007	<0.001	0.02	1.36	<0.02	0.01	0.004	<0.01	<0.01	12.62	1.04	0.004	0.32	1.93
633604	Drill Core	1.60	<0.001	0.014	<0.02	0.02	<2	0.014	<0.001	<0.01	4.21	<0.02	<0.01	<0.001	<0.01	<0.01	5.67	1.47	0.006	0.26	2.48
633605	Drill Core	1.06	<0.001	0.010	<0.02	0.06	3	0.009	<0.001	0.02	3.06	<0.02	0.01	<0.001	<0.01	<0.01	9.55	1.13	0.003	0.17	1.66
633606	Drill Core	1.45	<0.001	0.009	0.11	<0.01	<2	0.007	<0.001	0.02	2.05	<0.02	0.01	<0.001	<0.01	<0.01	9.07	0.74	0.004	0.39	2.14
633607	Drill Core	0.60	<0.001	0.016	0.03	0.01	2	0.005	<0.001	0.03	4.03	<0.02	0.02	<0.001	<0.01	<0.01	18.74	0.53	0.002	0.21	1.05
633608	Drill Core	1.35	<0.001	0.006	<0.02	<0.01	<2	0.002	<0.001	0.06	2.09	<0.02	0.02	<0.001	<0.01	<0.01	27.25	0.94	0.002	0.16	0.66
633609	Drill Core	0.69	0.002	0.010	0.02	0.13	<2	0.007	<0.001	0.02	1.96	<0.02	<0.01	0.001	<0.01	<0.01	7.99	0.58	0.003	0.18	1.26
633610	Drill Core	0.56	0.003	0.008	2.59	12.08	3	0.007	<0.001	<0.01	3.98	<0.02	<0.01	0.052	<0.01	<0.01	1.07	0.05	0.002	0.06	0.90
633611	Drill Core	0.57	0.003	0.009	2.20	12.38	5	0.006	<0.001	<0.01	4.41	<0.02	<0.01	0.056	<0.01	<0.01	0.19	0.03	0.002	0.06	0.86
633612	Drill Core	0.51	<0.001	0.006	3.03	7.62	6	0.005	<0.001	<0.01	9.10	<0.02	<0.01	0.031	<0.01	<0.01	0.45	0.02	0.002	0.03	0.42
633613	Drill Core	0.54	<0.001	0.007	4.35	11.97	5	0.004	<0.001	<0.01	9.84	<0.02	<0.01	0.056	<0.01	<0.01	1.10	0.02	0.002	0.02	0.38
633614	Drill Core	0.96	0.001	0.006	4.01	8.30	4	0.005	<0.001	0.02	5.77	<0.02	<0.01	0.032	<0.01	<0.01	2.97	0.04	0.002	0.04	0.57
633615	Drill Core	0.67	<0.001	<0.001	0.24	0.49	<2	0.002	<0.001	0.04	0.55	<0.02	0.01	0.002	<0.01	<0.01	23.30	0.03	<0.001	0.06	0.18
633616	Drill Core	0.50	0.004	0.006	5.80	4.65	2	0.009	<0.001	<0.01	2.71	<0.02	<0.01	0.012	<0.01	<0.01	1.30	0.05	0.002	0.08	1.08
633617	Drill Core	1.20	<0.001	0.004	0.94	2.85	<2	0.002	<0.001	0.05	1.87	<0.02	0.01	0.009	<0.01	<0.01	26.64	0.03	<0.001	0.07	0.19
633618	Drill Core	0.68	<0.001	0.002	<0.02	<0.01	<2	<0.001	<0.001	0.04	0.09	<0.02	0.01	<0.001	<0.01	<0.01	37.42	<0.01	<0.001	0.04	<0.01
633619	Drill Core	0.42	<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	0.04	0.18	<0.02	0.01	<0.001	<0.01	<0.01	37.28	0.02	<0.001	0.05	<0.01
633620	Rock	0.40	<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	0.02	0.20	<0.02	0.01	<0.001	<0.01	<0.01	21.32	0.03	<0.001	11.20	0.14
633621	Drill Core	0.79	0.005	0.027	1.07	0.24	7	0.013	<0.001	0.02	4.73	<0.02	<0.01	<0.001	<0.01	<0.01	13.66	0.26	0.004	0.14	0.96
633622	Drill Core	1.31	0.003	0.005	0.04	0.21	<2	0.006	<0.001	0.03	3.36	<0.02	0.02	<0.001	<0.01	<0.01	12.88	0.06	0.004	3.85	3.11
633623	Rock Pulp	0.04	<0.001	0.683	6.24	6.83	69	<0.001	0.001	0.09	4.92	<0.02	0.02	0.018	0.02	<0.01	1.39	0.02	0.001	0.25	5.19



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: January 10, 2011

Page: 2 of 2 **Part** 2

CERTIFICATE OF ANALYSIS

WHI10000703.1

	Method	7TD	7TD	7TD	7TD	G8SG
	Analyte	Na	K	W	S	SG
	Unit	%	%	%	%	
	MDL	0.01	0.01	0.01	0.05	0
633601	Drill Core	0.03	0.69	<0.01	4.22	2.58
633602	Drill Core	<0.01	1.58	<0.01	1.85	2.30
633603	Drill Core	<0.01	1.13	<0.01	1.82	2.45
633604	Drill Core	<0.01	1.53	<0.01	4.59	2.43
633605	Drill Core	<0.01	1.15	<0.01	3.34	2.48
633606	Drill Core	<0.01	1.48	<0.01	2.05	2.40
633607	Drill Core	<0.01	0.59	<0.01	4.57	2.56
633608	Drill Core	<0.01	0.41	<0.01	2.39	2.58
633609	Drill Core	<0.01	0.76	<0.01	2.10	2.45
633610	Drill Core	0.06	0.57	<0.01	10.25	2.74
633611	Drill Core	0.06	0.55	<0.01	10.79	2.76
633612	Drill Core	0.04	0.24	<0.01	13.74	2.83
633613	Drill Core	0.06	0.20	<0.01	16.79	2.99
633614	Drill Core	0.04	0.34	<0.01	10.69	2.77
633615	Drill Core	<0.01	0.08	<0.01	0.86	2.52
633616	Drill Core	0.02	0.72	<0.01	5.68	2.59
633617	Drill Core	0.02	0.11	<0.01	3.68	2.67
633618	Drill Core	<0.01	<0.01	<0.01	<0.05	2.67
633619	Drill Core	<0.01	0.02	<0.01	0.15	2.58
633620	Rock	0.01	0.03	<0.01	<0.05	2.67
633621	Drill Core	<0.01	0.55	<0.01	6.04	2.50
633622	Drill Core	<0.01	2.36	<0.01	2.89	2.57
633623	Rock Pulp	2.25	1.41	<0.01	6.18	N.A.



Acme Analytical Laboratories (Vancouver) Ltd.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: **Selwyn Resources Ltd.**

Suite 700 - 509 Richards Street

Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: January 10, 2011

Page: 1 of 1 Part 1

QUALITY CONTROL REPORT

WHI10000703.1

	Method Analyte Unit MDL	WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD
		Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg	Al
		kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%	%
		0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01	0.01
Pulp Duplicates																					
633611	Drill Core	0.57	0.003	0.009	2.20	12.38	5	0.006	<0.001	<0.01	4.41	<0.02	<0.01	0.056	<0.01	<0.01	0.19	0.03	0.002	0.06	0.86
REP 633611	QC		0.003	0.009	2.26	12.60	5	0.007	<0.001	<0.01	4.50	<0.02	<0.01	0.057	<0.01	<0.01	0.21	0.04	0.002	0.06	0.89
Reference Materials																					
STD OREAS131A	Standard		<0.001	0.036	1.77	2.95	31	0.002	0.002	0.17	5.81	<0.02	<0.01	0.008	<0.01	<0.01	5.32	0.06	0.002	3.16	4.69
STD OREAS131A	Standard		<0.001	0.033	1.77	2.87	30	0.003	0.002	0.17	5.97	<0.02	<0.01	0.009	<0.01	<0.01	5.37	0.06	0.002	3.14	4.61
STD R4T	Standard		0.064	0.509	1.57	3.49	88	0.356	0.041	0.09	24.00	<0.02	0.02	0.018	0.02	<0.01	2.20	0.05	0.015	1.42	3.98
STD R4T	Standard		0.062	0.495	1.52	3.34	86	0.349	0.040	0.09	23.92	<0.02	0.02	0.019	0.02	<0.01	2.14	0.05	0.017	1.37	3.85
STD SU-1B	Standard		<0.001	1.189	<0.02	0.03	7	1.976	0.066	0.07	25.07	<0.02	0.03	<0.001	<0.01	<0.01	2.23	0.06	0.027	1.80	4.42
STD SU-1B	Standard		<0.001	1.170	<0.02	0.03	10	1.984	0.068	0.07	25.62	<0.02	0.03	<0.001	<0.01	<0.01	2.22	0.07	0.031	1.78	4.37
STD R4T Expected			0.062	0.502	1.518	3.376	86	0.339	0.039	0.086	24.07	0.0087	0.0185	0.018	0.0138	0.0018	2.166	0.045	0.018	1.384	3.897
STD OREAS131A Expected			0.001	0.0322	1.72	2.83	30.9	0.0027	0.0023	0.1722	5.8166	0.0082	0.0028	0.0081	0.0047	0.001	5.286	0.0536	0.0025	3.1182	4.6057
STD SU-1B Expected			0.0004	1.185	0.0058	0.0235	6.4	1.97	0.0672	0.0703	25.54	0.00025	0.03	0.0003	0.00002	0.0003	2.21	0.06	0.032	1.79	4.39
BLK	Blank		<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	<0.01	<0.01	<0.02	<0.01	<0.001	<0.01	<0.01	<0.01	<0.01	<0.001	<0.01	<0.01
BLK	Blank		<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	<0.01	<0.01	<0.02	<0.01	<0.001	<0.01	<0.01	<0.01	<0.01	<0.001	<0.01	<0.01
Prep Wash																					
G1	Prep Blank		<0.001	<0.001	<0.02	0.01	<2	<0.001	<0.001	0.07	2.35	<0.02	0.07	<0.001	<0.01	<0.01	2.34	0.08	0.001	0.61	7.34
G1	Prep Blank		<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	0.07	2.38	<0.02	0.07	<0.001	<0.01	<0.01	2.39	0.08	0.001	0.61	7.44



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: January 10, 2011

Page: 1 of 1 **Part** 2

QUALITY CONTROL REPORT

WHI10000703.1

Method		7TD	7TD	7TD	7TD	G8SG
Analyte		Na	K	W	S	SG
Unit		%	%	%	%	%
MDL		0.01	0.01	0.01	0.05	0
Pulp Duplicates						
633611	Drill Core	0.06	0.55	<0.01	10.79	2.76
REP 633611	QC	0.06	0.57	<0.01	11.13	
Reference Materials						
STD OREAS131A	Standard	0.15	3.44	<0.01	4.86	
STD OREAS131A	Standard	0.16	3.26	<0.01	4.82	
STD R4T	Standard	0.91	1.18	<0.01	14.11	
STD R4T	Standard	0.89	1.14	<0.01	11.83	
STD SU-1B	Standard	1.67	0.60	0.01	10.67	
STD SU-1B	Standard	1.67	0.61	<0.01	8.15	
STD R4T Expected		0.9	1.153	0.00016	12.9903	
STD OREAS131A Expected		0.1501	3.1584	0.0005	4.8	
STD SU-1B Expected		1.662	0.6	0.0007	8.76	
BLK	Blank	<0.01	<0.01	<0.01	<0.05	
BLK	Blank	<0.01	<0.01	<0.01	<0.05	
Prep Wash						
G1	Prep Blank	2.63	2.94	<0.01	<0.05	2.71
G1	Prep Blank	2.63	2.88	<0.01	<0.05	2.70



1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: Selwyn Resources Ltd.

Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Submitted By: Jason K. Dunning

Receiving Lab: Canada-Whitehorse

Received: December 20, 2010

Report Date: January 10, 2011

Page: 1 of 2

CERTIFICATE OF ANALYSIS

WHI10000702.1

CLIENT JOB INFORMATION

Project: Selwyn Project
Shipment ID:
P.O. Number 1167
Number of Samples: 15

SAMPLE DISPOSAL

STOR-PLP Store After 90 days Invoice for Storage
STOR-RJT Store After 90 days Invoice for Storage

Acme does not accept responsibility for samples left at the laboratory after 90 days without prior written instructions for sample storage or return.

Invoice To: Selwyn Resources Ltd.
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6
Canada

CC:

SAMPLE PREPARATION AND ANALYTICAL PROCEDURES

Method Code	Number of Samples	Code Description	Test Wgt (g)	Report Status	Lab
R200-250	14	Crush split and pulverize 250g drill core to 200 mesh			WHI
7TD2	15	4 Acid digestion ICP-ES analysis.	0.5	Completed	VAN
G812	15	Specific Gravity on Pulp		Completed	VAN

ADDITIONAL COMMENTS



This report supersedes all previous preliminary and final reports with this file number dated prior to the date on this certificate. Signature indicates final approval; preliminary reports are unsigned and should be used for reference only.
All results are considered the confidential property of the client. Acme assumes the liabilities for actual cost of analysis only.
** asterisk indicates that an analytical result could not be provided due to unusually high levels of interference from other elements.



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: Selwyn Resources Ltd.
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: January 10, 2011

Page: 2 of 2 **Part** 1

CERTIFICATE OF ANALYSIS

WHI10000702.1

	Method Analyte Unit MDL	WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD
		Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg	Al
		kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%	%
		0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01	0.01
632401	Drill Core	1.51	0.002	0.006	0.04	0.15	<2	0.011	<0.001	0.02	2.19	<0.02	<0.01	0.001	<0.01	<0.01	7.31	0.13	0.008	0.32	2.66
632402	Drill Core	0.65	0.006	0.004	0.77	1.87	<2	0.012	<0.001	0.01	2.38	<0.02	<0.01	0.006	<0.01	<0.01	3.41	0.05	0.008	0.17	1.47
632403	Drill Core	1.00	0.001	0.004	4.03	16.36	<2	0.003	<0.001	0.03	2.07	<0.02	<0.01	0.045	<0.01	<0.01	11.02	0.05	0.001	0.08	0.48
632404	Drill Core	1.08	0.001	0.003	1.17	6.34	<2	0.004	<0.001	0.02	2.01	<0.02	<0.01	0.016	<0.01	<0.01	4.47	0.05	0.001	0.08	0.57
632405	Drill Core	0.90	0.003	0.006	1.84	7.15	<2	0.009	<0.001	0.03	5.40	<0.02	<0.01	0.015	<0.01	<0.01	7.52	0.09	0.002	0.12	0.97
632406	Drill Core	1.30	0.001	0.003	1.42	8.87	<2	0.005	<0.001	0.03	1.92	<0.02	<0.01	0.021	<0.01	<0.01	12.66	0.09	<0.001	0.09	0.55
632407	Drill Core	0.83	<0.001	0.002	2.89	8.92	<2	0.001	<0.001	0.03	0.98	<0.02	0.02	0.027	<0.01	<0.01	23.47	0.02	<0.001	0.05	0.16
632408	Drill Core	0.82	<0.001	0.003	2.93	17.73	<2	0.003	<0.001	0.02	1.55	<0.02	<0.01	0.043	<0.01	<0.01	9.10	0.04	<0.001	0.05	0.32
632409	Drill Core	0.88	<0.001	0.004	5.35	7.61	2	0.002	<0.001	0.03	1.77	<0.02	<0.01	0.034	<0.01	<0.01	13.27	0.03	<0.001	0.07	0.31
632410	Drill Core	0.52	0.002	0.008	0.04	0.07	<2	0.013	<0.001	0.01	2.52	<0.02	<0.01	<0.001	<0.01	<0.01	4.06	0.30	0.010	0.69	5.28
632411	Drill Core	0.55	0.001	0.007	0.02	0.08	<2	0.012	<0.001	0.01	2.35	<0.02	<0.01	<0.001	<0.01	<0.01	4.12	0.30	0.010	0.68	5.50
632412	Drill Core	1.76	0.003	0.008	<0.02	0.04	<2	0.017	<0.001	0.01	2.64	<0.02	<0.01	<0.001	<0.01	<0.01	4.51	0.16	0.012	0.57	5.32
632413	Rock	0.42	<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	0.01	0.14	<0.02	<0.01	<0.001	<0.01	<0.01	21.10	0.03	<0.001	10.78	0.11
632414	Drill Core	1.31	0.001	0.007	<0.02	0.01	<2	0.013	<0.001	0.01	2.09	<0.02	<0.01	<0.001	<0.01	<0.01	5.34	0.59	0.010	0.64	4.91
632415	Rock Pulp	0.06	<0.001	0.461	1.40	2.89	20	<0.001	<0.001	0.42	2.69	<0.02	0.02	0.018	<0.01	<0.01	4.74	0.02	0.002	0.31	4.06



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**

Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: January 10, 2011

Page: 2 of 2 Part 2

CERTIFICATE OF ANALYSIS

WHI10000702.1

	Method	7TD	7TD	7TD	7TD	G8SG
	Analyte	Na	K	W	S	SG
	Unit	%	%	%	%	
	MDL	0.01	0.01	0.01	0.05	0
632401	Drill Core	<0.01	1.50	<0.01	2.33	2.32
632402	Drill Core	<0.01	0.87	<0.01	3.58	2.27
632403	Drill Core	0.07	0.25	<0.01	11.02	2.77
632404	Drill Core	0.03	0.33	<0.01	5.40	2.56
632405	Drill Core	0.03	0.55	<0.01	9.73	2.61
632406	Drill Core	0.04	0.29	<0.01	6.76	2.63
632407	Drill Core	0.04	0.08	<0.01	5.84	2.74
632408	Drill Core	0.07	0.15	<0.01	10.67	2.79
632409	Drill Core	0.03	0.15	<0.01	6.59	2.72
632410	Drill Core	<0.01	2.45	<0.01	2.50	2.26
632411	Drill Core	<0.01	2.66	<0.01	2.31	2.27
632412	Drill Core	<0.01	3.22	<0.01	2.65	2.18
632413	Rock	<0.01	0.02	<0.01	<0.05	2.65
632414	Drill Core	<0.01	2.85	<0.01	2.05	2.29
632415	Rock Pulp	1.65	1.24	<0.01	3.20	N.A.



Acme Analytical Laboratories (Vancouver) Ltd.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: **Selwyn Resources Ltd.**

Suite 700 - 509 Richards Street

Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: January 10, 2011

Page: 1 of 1 Part 1

QUALITY CONTROL REPORT

WHI10000702.1

	Method Analyte Unit MDL	WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD
		Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg	Al
		kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%	%
		0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01	0.01
Core Reject Duplicates																					
632411	Drill Core	0.55	0.001	0.007	0.02	0.08	<2	0.012	<0.001	0.01	2.35	<0.02	<0.01	<0.001	<0.01	<0.01	4.12	0.30	0.010	0.68	5.50
DUP 632411	QC		0.001	0.008	0.02	0.08	<2	0.012	0.001	0.01	2.32	<0.02	<0.01	<0.001	<0.01	<0.01	4.12	0.29	0.010	0.68	5.51
Reference Materials																					
STD OREAS131A	Standard		<0.001	0.032	1.71	2.90	30	0.002	0.002	0.17	5.89	<0.02	<0.01	0.008	<0.01	<0.01	5.46	0.05	0.002	3.21	4.75
STD OREAS131A	Standard		<0.001	0.033	1.77	2.87	30	0.003	0.002	0.17	5.97	<0.02	<0.01	0.009	<0.01	<0.01	5.37	0.06	0.002	3.14	4.61
STD R4T	Standard		0.065	0.514	1.59	3.44	86	0.357	0.041	0.09	24.28	<0.02	0.02	0.019	0.02	<0.01	2.25	0.04	0.019	1.45	4.08
STD R4T	Standard		0.062	0.495	1.52	3.34	86	0.349	0.040	0.09	23.92	<0.02	0.02	0.019	0.02	<0.01	2.14	0.05	0.017	1.37	3.85
STD SU-1B	Standard		<0.001	1.207	<0.02	0.03	6	1.990	0.067	0.07	25.29	<0.02	0.03	<0.001	<0.01	<0.01	2.27	0.06	0.031	1.82	4.49
STD SU-1B	Standard		<0.001	1.170	<0.02	0.03	10	1.984	0.068	0.07	25.62	<0.02	0.03	<0.001	<0.01	<0.01	2.22	0.07	0.031	1.78	4.37
STD R4T Expected			0.062	0.502	1.518	3.376	86	0.339	0.039	0.086	24.07	0.0087	0.0185	0.018	0.0138	0.0018	2.166	0.045	0.018	1.384	3.897
STD OREAS131A Expected			0.001	0.0322	1.72	2.83	30.9	0.0027	0.0023	0.1722	5.8166	0.0082	0.0028	0.0081	0.0047	0.001	5.286	0.0536	0.0025	3.1182	4.6057
STD SU-1B Expected			0.0004	1.185	0.0058	0.0235	6.4	1.97	0.0672	0.0703	25.54	0.00025	0.03	0.0003	0.00002	0.0003	2.21	0.06	0.032	1.79	4.39
BLK	Blank		<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	<0.01	<0.01	<0.02	<0.01	<0.001	<0.01	<0.01	<0.01	<0.01	<0.001	<0.01	<0.01
BLK	Blank		<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	<0.01	<0.01	<0.02	<0.01	<0.001	<0.01	<0.01	<0.01	<0.01	<0.001	<0.01	<0.01
Prep Wash																					
G1	Prep Blank		<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	0.07	2.29	<0.02	0.07	<0.001	<0.01	<0.01	2.37	0.08	0.002	0.65	7.81
G1	Prep Blank		<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	0.08	2.34	<0.02	0.07	<0.001	<0.01	<0.01	2.36	0.08	0.001	0.66	7.66



Acme Analytical Laboratories (Vancouver) Ltd.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: **Selwyn Resources Ltd.**

Suite 700 - 509 Richards Street

Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: January 10, 2011

Page: 1 of 1 **Part** 2

QUALITY CONTROL REPORT

WHI10000702.1

Method		7TD	7TD	7TD	7TD	G8SG
Analyte		Na	K	W	S	SG
Unit		%	%	%	%	%
MDL		0.01	0.01	0.01	0.05	0
Core Reject Duplicates						
632411	Drill Core	<0.01	2.66	<0.01	2.31	2.27
DUP 632411	QC	<0.01	2.75	<0.01	2.31	2.26
Reference Materials						
STD OREAS131A	Standard	0.16	3.45	<0.01	4.83	
STD OREAS131A	Standard	0.16	3.26	<0.01	4.82	
STD R4T	Standard	0.94	1.36	<0.01	12.41	
STD R4T	Standard	0.89	1.14	<0.01	11.83	
STD SU-1B	Standard	1.72	0.62	<0.01	8.67	
STD SU-1B	Standard	1.67	0.61	<0.01	8.15	
STD R4T Expected		0.9	1.153	0.00016	12.9903	
STD OREAS131A Expected		0.1501	3.1584	0.0005	4.8	
STD SU-1B Expected		1.662	0.6	0.0007	8.76	
BLK	Blank	<0.01	0.05	<0.01	<0.05	
BLK	Blank	<0.01	<0.01	<0.01	<0.05	
Prep Wash						
G1	Prep Blank	2.68	3.00	<0.01	<0.05	2.70
G1	Prep Blank	2.70	3.02	<0.01	<0.05	2.68



1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: Selwyn Resources Ltd.

Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Submitted By: Jason K. Dunning

Receiving Lab: Canada-Whitehorse

Received: December 20, 2010

Report Date: January 07, 2011

Page: 1 of 2

CERTIFICATE OF ANALYSIS

WHI10000701.1

CLIENT JOB INFORMATION

Project: Selwyn Project
Shipment ID:
P.O. Number 1167
Number of Samples: 4

SAMPLE DISPOSAL

STOR-PLP Store After 90 days Invoice for Storage
STOR-RJT Store After 90 days Invoice for Storage

Acme does not accept responsibility for samples left at the laboratory after 90 days without prior written instructions for sample storage or return.

Invoice To: Selwyn Resources Ltd.
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6
Canada

CC:

SAMPLE PREPARATION AND ANALYTICAL PROCEDURES

Method Code	Number of Samples	Code Description	Test Wgt (g)	Report Status	Lab
R200-250	4	Crush split and pulverize 250g drill core to 200 mesh			WHI
7TD2	4	4 Acid digestion ICP-ES analysis.	0.5	Completed	VAN
G812	4	Specific Gravity on Pulp		Completed	VAN

ADDITIONAL COMMENTS



This report supersedes all previous preliminary and final reports with this file number dated prior to the date on this certificate. Signature indicates final approval; preliminary reports are unsigned and should be used for reference only.

All results are considered the confidential property of the client. Acme assumes the liabilities for actual cost of analysis only.

“**” asterisk indicates that an analytical result could not be provided due to unusually high levels of interference from other elements.



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: January 07, 2011

Page: 2 of 2 **Part** 1

CERTIFICATE OF ANALYSIS

WHI10000701.1

	Method	WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD
	Analyte	Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg
	Unit	kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%
	MDL	0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01
633082	Drill Core	1.08	<0.001	0.006	0.14	0.98	<2	0.012	<0.001	0.01	1.63	<0.02	0.01	0.003	<0.01	<0.01	6.66	1.52	0.009	0.59
633083	Drill Core	1.03	<0.001	0.005	0.03	0.12	<2	0.012	<0.001	<0.01	1.53	<0.02	0.01	<0.001	<0.01	<0.01	7.38	2.24	0.011	0.67
633084	Drill Core	1.46	<0.001	0.008	0.46	3.22	3	0.010	<0.001	0.02	2.60	<0.02	0.02	0.009	<0.01	<0.01	11.09	1.59	0.008	0.48
633085	Drill Core	1.53	<0.001	0.004	0.08	0.36	<2	0.010	<0.001	0.01	1.34	<0.02	0.01	0.001	<0.01	<0.01	9.29	1.57	0.009	0.59



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**

Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: January 07, 2011

Page: 2 of 2 **Part** 2

CERTIFICATE OF ANALYSIS

WHI10000701.1

	Method	7TD	7TD	7TD	7TD	G8SG
	Analyte	Na	K	W	S	SG
	Unit	%	%	%	%	
	MDL	0.01	0.01	0.01	0.05	0
633082	Drill Core	<0.01	2.22	<0.01	2.15	2.15
633083	Drill Core	0.01	2.35	<0.01	1.57	2.03
633084	Drill Core	<0.01	1.88	<0.01	4.60	2.24
633085	Drill Core	<0.01	1.90	<0.01	1.53	2.13



Acme Analytical Laboratories (Vancouver) Ltd.
1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: January 07, 2011

Page: 1 of 1 Part 1

QUALITY CONTROL REPORT

WHI10000701.1

	Method Analyte Unit MDL	WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD
		Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg	Al
		kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%	%
		0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01	0.01
Pulp Duplicates																					
633083	Drill Core	1.03	<0.001	0.005	0.03	0.12	<2	0.012	<0.001	<0.01	1.53	<0.02	0.01	<0.001	<0.01	<0.01	7.38	2.24	0.011	0.67	3.58
REP 633083	QC		<0.001	0.005	0.04	0.12	<2	0.013	<0.001	<0.01	1.54	<0.02	0.01	<0.001	<0.01	<0.01	7.46	2.26	0.010	0.68	3.61
Core Reject Duplicates																					
633082	Drill Core	1.08	<0.001	0.006	0.14	0.98	<2	0.012	<0.001	0.01	1.63	<0.02	0.01	0.003	<0.01	<0.01	6.66	1.52	0.009	0.59	3.38
DUP 633082	QC		<0.001	0.006	0.12	0.92	2	0.012	<0.001	0.01	1.58	<0.02	0.01	0.003	<0.01	<0.01	6.89	1.52	0.008	0.58	3.34
Reference Materials																					
STD OREAS131A	Standard		<0.001	0.032	1.71	2.90	30	0.002	0.002	0.17	5.89	<0.02	<0.01	0.008	<0.01	<0.01	5.46	0.05	0.002	3.21	4.75
STD R4T	Standard		0.065	0.514	1.59	3.44	86	0.357	0.041	0.09	24.28	<0.02	0.02	0.019	0.02	<0.01	2.25	0.04	0.019	1.45	4.08
STD SU-1B	Standard		<0.001	1.207	<0.02	0.03	6	1.990	0.067	0.07	25.29	<0.02	0.03	<0.001	<0.01	<0.01	2.27	0.06	0.031	1.82	4.49
STD R4T Expected			0.062	0.502	1.518	3.376	86	0.339	0.039	0.086	24.07	0.0087	0.0185	0.018	0.0138	0.0018	2.166	0.045	0.018	1.384	3.897
STD OREAS131A Expected			0.001	0.0322	1.72	2.83	30.9	0.0027	0.0023	0.1722	5.8166	0.0082	0.0028	0.0081	0.0047	0.001	5.286	0.0536	0.0025	3.1182	4.6057
STD SU-1B Expected			0.0004	1.185	0.0058	0.0235	6.4	1.97	0.0672	0.0703	25.54	0.00025	0.03	0.0003	0.00002	0.0003	2.21	0.06	0.032	1.79	4.39
BLK	Blank		<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	<0.01	<0.01	<0.02	<0.01	<0.001	<0.01	<0.01	<0.01	<0.01	<0.001	<0.01	<0.01
Prep Wash																					
G1	Prep Blank		<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	0.08	2.37	<0.02	0.08	<0.001	<0.01	<0.01	2.42	0.08	0.001	0.67	7.63
G1	Prep Blank		<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	0.08	2.35	<0.02	0.08	<0.001	<0.01	<0.01	2.37	0.08	0.001	0.65	7.90



Acme Analytical Laboratories (Vancouver) Ltd.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: **Selwyn Resources Ltd.**

Suite 700 - 509 Richards Street

Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: January 07, 2011

Page: 1 of 1 **Part** 2

QUALITY CONTROL REPORT

WHI10000701.1

		Method	7TD	7TD	7TD	7TD	G8SG
		Analyte	Na	K	W	S	SG
		Unit	%	%	%	%	
		MDL	0.01	0.01	0.01	0.05	0
Pulp Duplicates							
633083	Drill Core		0.01	2.35	<0.01	1.57	2.03
REP 633083	QC		0.01	2.35	<0.01	1.58	
Core Reject Duplicates							
633082	Drill Core		<0.01	2.22	<0.01	2.15	2.15
DUP 633082	QC		0.01	2.59	<0.01	2.07	2.06
Reference Materials							
STD OREAS131A	Standard		0.16	3.45	<0.01	4.83	
STD R4T	Standard		0.94	1.36	<0.01	12.41	
STD SU-1B	Standard		1.72	0.62	<0.01	8.67	
STD R4T Expected			0.9	1.153	0.00016	12.9903	
STD OREAS131A Expected			0.1501	3.1584	0.0005	4.8	
STD SU-1B Expected			1.662	0.6	0.0007	8.76	
BLK	Blank		<0.01	0.05	<0.01	<0.05	
Prep Wash							
G1	Prep Blank		2.89	3.16	<0.01	<0.05	2.73
G1	Prep Blank		2.84	3.10	<0.01	<0.05	2.70



1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: Selwyn Resources Ltd.

Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Submitted By: Jason K. Dunning

Receiving Lab: Canada-Whitehorse

Received: December 20, 2010

Report Date: January 07, 2011

Page: 1 of 2

CERTIFICATE OF ANALYSIS

WHI10000700.1

CLIENT JOB INFORMATION

Project: Selwyn Project
Shipment ID:
P.O. Number 1167
Number of Samples: 23

SAMPLE DISPOSAL

STOR-PLP Store After 90 days Invoice for Storage
STOR-RJT Store After 90 days Invoice for Storage

Acme does not accept responsibility for samples left at the laboratory after 90 days without prior written instructions for sample storage or return.

Invoice To: Selwyn Resources Ltd.
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6
Canada

CC:

SAMPLE PREPARATION AND ANALYTICAL PROCEDURES

Method Code	Number of Samples	Code Description	Test Wgt (g)	Report Status	Lab
R200-250	22	Crush split and pulverize 250g drill core to 200 mesh			WHI
7TD2	23	4 Acid digestion ICP-ES analysis.	0.5	Completed	VAN
G812	23	Specific Gravity on Pulp		Completed	VAN

ADDITIONAL COMMENTS



This report supersedes all previous preliminary and final reports with this file number dated prior to the date on this certificate. Signature indicates final approval; preliminary reports are unsigned and should be used for reference only.
All results are considered the confidential property of the client. Acme assumes the liabilities for actual cost of analysis only.
** asterisk indicates that an analytical result could not be provided due to unusually high levels of interference from other elements.



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: January 07, 2011

Page: 2 of 2 Part 1

CERTIFICATE OF ANALYSIS

WHI10000700.1

	Method Analyte Unit MDL	WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	
		Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg	Al
		kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%	%
		0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01	0.01
633801	Drill Core	2.02	0.002	0.007	<0.02	0.12	<2	0.008	<0.001	<0.01	1.43	<0.02	<0.01	<0.001	<0.01	<0.01	4.13	0.88	0.004	0.13	1.17
633802	Drill Core	1.19	<0.001	0.002	0.41	0.64	<2	0.003	<0.001	0.05	0.54	<0.02	0.02	0.003	<0.01	<0.01	22.16	0.11	0.001	0.11	0.34
633803	Drill Core	0.43	<0.001	0.002	<0.02	0.17	<2	0.001	<0.001	0.06	1.04	<0.02	0.01	<0.001	<0.01	<0.01	16.63	0.06	<0.001	0.08	0.27
633804	Drill Core	1.57	0.001	0.007	6.01	9.75	3	0.005	<0.001	<0.01	5.25	<0.02	<0.01	0.049	<0.01	<0.01	0.31	0.02	0.003	0.05	0.56
633805	Drill Core	1.26	0.002	0.005	0.92	4.06	<2	0.006	<0.001	0.03	6.61	<0.02	<0.01	0.012	<0.01	<0.01	8.78	0.04	0.002	0.07	0.53
633806	Drill Core	1.38	0.003	0.005	0.97	4.39	<2	0.009	<0.001	0.02	3.54	<0.02	<0.01	0.011	<0.01	<0.01	3.25	0.05	0.002	0.09	0.99
633807	Drill Core	0.43	<0.001	0.002	0.07	0.43	<2	0.001	<0.001	0.05	0.40	<0.02	0.02	<0.001	<0.01	<0.01	33.69	0.01	<0.001	0.08	0.02
633808	Drill Core	0.97	0.001	0.002	0.07	1.21	<2	0.003	<0.001	<0.01	1.29	<0.02	<0.01	0.003	<0.01	<0.01	1.96	0.03	0.001	0.04	0.39
633809	Drill Core	1.64	0.003	0.004	3.64	2.61	<2	0.008	<0.001	0.02	3.53	<0.02	<0.01	0.008	<0.01	<0.01	7.54	0.04	0.003	0.10	0.96
633810	Drill Core	0.89	<0.001	0.003	2.43	6.22	<2	0.003	<0.001	0.04	1.91	<0.02	0.01	0.023	<0.01	<0.01	19.19	0.04	0.001	0.08	0.28
633811	Drill Core	0.79	0.001	0.003	1.06	3.84	<2	0.004	<0.001	0.05	2.25	<0.02	0.02	0.011	<0.01	<0.01	23.38	0.03	0.001	0.09	0.30
633812	Drill Core	1.23	0.003	0.007	0.19	0.77	<2	0.006	<0.001	0.03	0.62	<0.02	0.02	0.002	<0.01	<0.01	19.05	0.25	0.002	0.10	0.52
633813	Drill Core	1.06	0.002	0.006	0.07	0.19	<2	0.006	<0.001	0.02	0.31	<0.02	0.01	<0.001	<0.01	<0.01	15.27	0.22	0.001	0.07	0.38
633814	Drill Core	1.47	0.005	0.009	0.27	1.64	2	0.012	<0.001	0.01	1.19	<0.02	<0.01	0.004	<0.01	<0.01	8.07	0.30	0.004	0.12	0.88
633815	Drill Core	1.54	0.006	0.025	0.56	0.74	4	0.014	<0.001	0.01	6.78	<0.02	<0.01	0.002	<0.01	<0.01	7.04	0.12	0.005	0.12	0.88
633816	Drill Core	1.55	0.006	0.011	0.19	1.11	5	0.029	<0.001	<0.01	1.37	<0.02	<0.01	0.003	<0.01	<0.01	7.61	2.26	0.017	0.23	1.93
633817	Drill Core	1.60	<0.001	0.006	0.64	0.58	5	0.021	<0.001	<0.01	1.12	<0.02	0.01	0.002	<0.01	<0.01	10.95	3.09	0.017	0.23	1.96
633818	Drill Core	0.29	0.001	0.004	2.43	0.20	11	0.012	<0.001	0.01	3.04	<0.02	<0.01	<0.001	<0.01	<0.01	8.33	1.64	0.008	0.44	3.68
633819	Drill Core	2.69	<0.001	0.002	0.03	<0.01	<2	0.003	<0.001	0.03	2.23	<0.02	0.02	<0.001	<0.01	<0.01	21.30	0.07	0.003	0.39	2.67
633820	Rock	0.22	<0.001	<0.001	<0.02	<0.01	<2	0.001	<0.001	0.03	0.36	<0.02	0.01	<0.001	<0.01	<0.01	21.65	0.03	0.001	10.88	0.35
633821	Drill Core	2.57	<0.001	0.002	<0.02	<0.01	<2	0.004	<0.001	0.05	1.58	<0.02	0.02	<0.001	<0.01	<0.01	26.38	0.03	0.002	0.35	2.52
633822	Drill Core	2.36	0.007	0.010	<0.02	<0.01	2	0.018	0.001	0.01	4.17	<0.02	0.01	<0.001	<0.01	<0.01	11.40	2.29	0.011	0.36	3.04
633823	Rock Pulp	0.06	<0.001	0.496	1.44	2.95	16	<0.001	<0.001	0.45	2.65	<0.02	0.02	0.018	<0.01	<0.01	5.01	0.01	0.001	0.34	4.36



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**

Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: January 07, 2011

Page: 2 of 2 **Part** 2

CERTIFICATE OF ANALYSIS

WHI10000700.1

	Method	7TD	7TD	7TD	7TD	G8SG
	Analyte	Na	K	W	S	SG
	Unit	%	%	%	%	
	MDL	0.01	0.01	0.01	0.05	0
633801	Drill Core	<0.01	0.83	<0.01	1.59	2.33
633802	Drill Core	<0.01	0.19	<0.01	0.94	2.49
633803	Drill Core	<0.01	0.17	<0.01	1.21	2.55
633804	Drill Core	<0.01	0.33	<0.01	11.95	2.85
633805	Drill Core	<0.01	0.32	<0.01	10.09	2.66
633806	Drill Core	<0.01	0.74	<0.01	6.54	2.39
633807	Drill Core	<0.01	0.08	<0.01	0.64	2.53
633808	Drill Core	<0.01	0.46	<0.01	1.89	2.46
633809	Drill Core	<0.01	0.59	<0.01	6.19	2.51
633810	Drill Core	<0.01	0.16	<0.01	5.80	2.63
633811	Drill Core	<0.01	0.17	<0.01	4.63	2.58
633812	Drill Core	<0.01	0.30	<0.01	1.07	2.39
633813	Drill Core	<0.01	0.21	<0.01	0.34	2.37
633814	Drill Core	<0.01	0.50	<0.01	2.18	2.27
633815	Drill Core	<0.01	0.53	<0.01	8.54	2.39
633816	Drill Core	<0.01	1.23	<0.01	2.14	1.83
633817	Drill Core	<0.01	1.40	<0.01	1.58	1.97
633818	Drill Core	<0.01	2.79	<0.01	3.86	2.51
633819	Drill Core	<0.01	1.70	<0.01	2.54	2.63
633820	Rock	0.03	0.06	<0.01	<0.05	2.65
633821	Drill Core	<0.01	1.67	<0.01	1.73	2.54
633822	Drill Core	<0.01	2.24	<0.01	4.84	2.19
633823	Rock Pulp	1.78	1.53	<0.01	3.29	N.A.



Acme Analytical Laboratories (Vancouver) Ltd.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: **Selwyn Resources Ltd.**

Suite 700 - 509 Richards Street

Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: January 07, 2011

Page: 1 of 1 Part 1

QUALITY CONTROL REPORT

WHI10000700.1

	Method Analyte Unit MDL	WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD
		Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg	Al
		kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%	%
		0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01	0.01
Core Reject Duplicates																					
633812	Drill Core	1.23	0.003	0.007	0.19	0.77	<2	0.006	<0.001	0.03	0.62	<0.02	0.02	0.002	<0.01	<0.01	19.05	0.25	0.002	0.10	0.52
DUP 633812	QC		0.003	0.007	0.21	0.81	<2	0.006	<0.001	0.03	0.64	<0.02	0.02	0.002	<0.01	<0.01	18.80	0.25	0.002	0.10	0.54
Reference Materials																					
STD OREAS131A	Standard		<0.001	0.032	1.71	2.90	30	0.002	0.002	0.17	5.89	<0.02	<0.01	0.008	<0.01	<0.01	5.46	0.05	0.002	3.21	4.75
STD R4T	Standard		0.065	0.514	1.59	3.44	86	0.357	0.041	0.09	24.28	<0.02	0.02	0.019	0.02	<0.01	2.25	0.04	0.019	1.45	4.08
STD SU-1B	Standard		<0.001	1.207	<0.02	0.03	6	1.990	0.067	0.07	25.29	<0.02	0.03	<0.001	<0.01	<0.01	2.27	0.06	0.031	1.82	4.49
STD R4T Expected			0.062	0.502	1.518	3.376	86	0.339	0.039	0.086	24.07	0.0087	0.0185	0.018	0.0138	0.0018	2.166	0.045	0.018	1.384	3.897
STD OREAS131A Expected			0.001	0.0322	1.72	2.83	30.9	0.0027	0.0023	0.1722	5.8166	0.0082	0.0028	0.0081	0.0047	0.001	5.286	0.0536	0.0025	3.1182	4.6057
STD SU-1B Expected			0.0004	1.185	0.0058	0.0235	6.4	1.97	0.0672	0.0703	25.54	0.00025	0.03	0.0003	0.00002	0.0003	2.21	0.06	0.032	1.79	4.39
BLK	Blank		<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	<0.01	<0.01	<0.02	<0.01	<0.001	<0.01	<0.01	<0.01	<0.01	<0.001	<0.01	<0.01
Prep Wash																					
G1	Prep Blank		<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	0.07	2.27	<0.02	0.07	<0.001	<0.01	<0.01	2.36	0.08	0.001	0.66	7.99
G1	Prep Blank		<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	0.07	2.33	<0.02	0.08	<0.001	<0.01	<0.01	2.43	0.08	0.001	0.69	8.02



Acme Analytical Laboratories (Vancouver) Ltd.
1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: January 07, 2011

Page: 1 of 1 **Part** 2

QUALITY CONTROL REPORT

WHI10000700.1

Method		7TD	7TD	7TD	7TD	G8SG
Analyte		Na	K	W	S	SG
Unit		%	%	%	%	%
MDL		0.01	0.01	0.01	0.05	0
Core Reject Duplicates						
633812	Drill Core	<0.01	0.30	<0.01	1.07	2.39
DUP 633812	QC	<0.01	0.31	<0.01	1.09	2.40
Reference Materials						
STD OREAS131A	Standard	0.16	3.45	<0.01	4.83	
STD R4T	Standard	0.94	1.36	<0.01	12.41	
STD SU-1B	Standard	1.72	0.62	<0.01	8.67	
STD R4T Expected		0.9	1.153	0.00016	12.9903	
STD OREAS131A Expected		0.1501	3.1584	0.0005	4.8	
STD SU-1B Expected		1.662	0.6	0.0007	8.76	
BLK	Blank	<0.01	0.05	<0.01	<0.05	
Prep Wash						
G1	Prep Blank	2.73	3.00	<0.01	<0.05	2.67
G1	Prep Blank	2.72	3.03	<0.01	<0.05	2.64



1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: Selwyn Resources Ltd.

Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Submitted By: Jason K. Dunning

Receiving Lab: Canada-Whitehorse

Received: December 16, 2010

Report Date: January 07, 2011

Page: 1 of 4

CERTIFICATE OF ANALYSIS

WHI10000694.1

CLIENT JOB INFORMATION

Project: Selwyn Project
Shipment ID:
P.O. Number 1163
Number of Samples: 64

SAMPLE DISPOSAL

STOR-PLP Store After 90 days Invoice for Storage
STOR-RJT Store After 90 days Invoice for Storage

Acme does not accept responsibility for samples left at the laboratory after 90 days without prior written instructions for sample storage or return.

Invoice To: Selwyn Resources Ltd.
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6
Canada

CC:

SAMPLE PREPARATION AND ANALYTICAL PROCEDURES

Method Code	Number of Samples	Code Description	Test Wgt (g)	Report Status	Lab
R200-250	62	Crush split and pulverize 250g drill core to 200 mesh			WHI
7TD2	64	4 Acid digestion ICP-ES analysis.	0.5	Completed	VAN
G812	64	Specific Gravity on Pulp		Completed	VAN

ADDITIONAL COMMENTS



This report supersedes all previous preliminary and final reports with this file number dated prior to the date on this certificate. Signature indicates final approval; preliminary reports are unsigned and should be used for reference only.

All results are considered the confidential property of the client. Acme assumes the liabilities for actual cost of analysis only.

“**” asterisk indicates that an analytical result could not be provided due to unusually high levels of interference from other elements.



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: January 07, 2011

Page: 2 of 4 Part 1

CERTIFICATE OF ANALYSIS

WHI10000694.1

	Method Analyte Unit MDL	WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD
		Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg	Al
		kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%	%
		0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01	0.01
633951	Drill Core	2.71	<0.001	0.005	0.06	0.32	<2	0.012	<0.001	0.01	1.65	<0.02	0.01	0.001	<0.01	<0.01	9.34	2.03	0.007	0.90	3.27
633952	Drill Core	3.46	<0.001	0.008	1.17	7.77	6	0.003	<0.001	0.02	3.36	<0.02	0.01	0.024	<0.01	<0.01	12.40	0.05	0.001	0.20	0.48
633953	Drill Core	2.78	<0.001	0.007	0.02	0.16	<2	0.013	<0.001	0.01	1.88	<0.02	<0.01	<0.001	<0.01	<0.01	6.89	1.94	0.007	0.75	3.44
633954	Drill Core	2.54	<0.001	0.002	<0.02	0.08	<2	0.003	<0.001	0.08	0.48	<0.02	0.02	<0.001	<0.01	<0.01	27.57	0.29	0.001	0.14	0.44
633955	Drill Core	1.11	0.003	0.004	0.18	0.33	<2	0.009	<0.001	<0.01	1.16	<0.02	<0.01	0.002	<0.01	<0.01	1.34	0.35	0.004	0.14	1.39
633956	Drill Core	3.28	0.005	0.012	1.16	8.46	4	0.012	<0.001	0.01	9.05	<0.02	<0.01	0.029	<0.01	<0.01	1.08	0.06	0.004	0.14	1.54
633957	Drill Core	0.68	0.001	0.005	2.19	12.18	<2	0.002	<0.001	<0.01	3.04	<0.02	<0.01	0.057	<0.01	<0.01	0.94	<0.01	<0.001	0.03	0.33
633958	Drill Core	1.32	0.003	0.011	2.39	8.05	23	0.008	<0.001	0.02	6.86	<0.02	<0.01	0.026	<0.01	<0.01	7.00	0.03	0.002	0.10	0.72
633959	Drill Core	0.99	<0.001	0.001	0.30	0.99	<2	0.002	<0.001	0.09	1.28	<0.02	0.02	0.002	<0.01	<0.01	31.17	0.03	<0.001	0.13	0.19
633960	Drill Core	0.56	0.003	0.007	1.38	7.83	7	0.008	<0.001	0.02	2.92	<0.02	<0.01	0.020	<0.01	<0.01	3.51	0.07	0.003	0.09	0.91
633961	Drill Core	0.67	0.003	0.014	1.43	6.24	47	0.007	<0.001	0.02	3.28	<0.02	<0.01	0.017	<0.01	<0.01	9.65	0.08	0.002	0.09	0.78
633962	Drill Core	1.73	0.001	0.001	0.08	0.44	<2	0.003	<0.001	0.02	2.59	<0.02	<0.01	<0.001	<0.01	<0.01	11.70	0.03	0.001	0.05	0.29
633963	Drill Core	0.73	0.001	0.001	0.05	0.62	<2	0.003	<0.001	0.01	0.76	<0.02	<0.01	<0.001	<0.01	<0.01	7.53	0.03	<0.001	0.04	0.31
633964	Drill Core	2.16	0.002	0.004	5.27	12.20	4	0.004	<0.001	0.03	2.46	<0.02	<0.01	0.042	<0.01	<0.01	14.71	0.04	0.001	0.06	0.35
633965	Drill Core	0.61	0.001	0.002	1.27	3.41	<2	0.004	<0.001	0.03	1.27	<0.02	0.01	0.011	<0.01	<0.01	15.64	0.04	0.001	0.08	0.51
633966	Drill Core	0.33	0.002	0.003	0.74	4.52	<2	0.006	<0.001	0.01	1.53	<0.02	<0.01	0.011	<0.01	<0.01	4.06	0.06	0.001	0.08	0.73
633967	Drill Core	3.69	0.002	0.003	1.01	4.41	<2	0.004	<0.001	0.03	1.26	<0.02	0.01	0.013	<0.01	<0.01	19.42	0.04	0.001	0.09	0.53
633968	Drill Core	3.02	0.002	0.004	0.05	0.02	<2	0.006	<0.001	0.03	1.48	<0.02	0.01	<0.001	<0.01	<0.01	18.28	0.06	0.002	0.13	0.81
633969	Drill Core	2.36	0.002	0.003	0.06	0.27	<2	0.004	<0.001	0.03	1.19	<0.02	0.01	<0.001	<0.01	<0.01	19.95	0.04	0.001	0.08	0.43
633970	Rock	0.40	<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	0.01	0.15	<0.02	0.01	<0.001	<0.01	<0.01	21.35	0.03	<0.001	11.36	0.18
633971	Drill Core	2.70	0.002	0.005	0.14	0.43	<2	0.005	<0.001	0.04	0.71	<0.02	0.02	<0.001	<0.01	<0.01	24.54	0.23	0.002	0.10	0.34
633972	Drill Core	0.82	0.007	0.013	0.36	1.33	<2	0.010	<0.001	0.02	0.80	<0.02	<0.01	0.002	<0.01	<0.01	9.79	0.60	0.005	0.18	0.96
633973	Drill Core	0.85	<0.001	0.002	<0.02	0.01	<2	0.002	<0.001	0.03	0.45	<0.02	0.02	<0.001	<0.01	<0.01	35.20	0.14	0.001	0.20	0.08
633974	Drill Core	2.43	0.008	0.017	0.21	1.90	<2	0.014	<0.001	0.01	1.09	<0.02	<0.01	0.004	<0.01	<0.01	7.99	0.38	0.006	0.15	1.16
633975	Drill Core	3.11	0.011	0.021	0.19	1.48	<2	0.020	<0.001	<0.01	2.98	<0.02	<0.01	0.004	<0.01	<0.01	3.59	0.21	0.005	0.16	1.36
633976	Drill Core	1.53	0.002	0.009	0.26	0.28	<2	0.023	<0.001	<0.01	2.89	<0.02	<0.01	<0.001	<0.01	<0.01	8.49	2.60	0.015	0.28	2.53
633977	Drill Core	2.84	<0.001	0.001	<0.02	0.03	<2	0.002	<0.001	0.04	1.49	<0.02	0.02	<0.001	<0.01	<0.01	24.61	0.02	0.002	0.37	2.34
633978	Drill Core	3.18	0.003	0.005	<0.02	0.03	<2	0.011	<0.001	0.03	2.75	<0.02	0.02	<0.001	<0.01	<0.01	18.60	2.28	0.006	0.36	2.80
633979	Drill Core	2.44	0.007	0.012	0.02	0.23	<2	0.028	<0.001	0.01	3.02	<0.02	<0.01	<0.001	<0.01	<0.01	5.87	0.20	0.016	0.41	3.95
633980	Rock Pulp	0.06	<0.001	0.472	1.42	2.91	19	<0.001	<0.001	0.43	2.68	<0.02	0.02	0.018	<0.01	<0.01	4.75	0.02	0.002	0.32	4.07



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**

Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: January 07, 2011

Page: 2 of 4 Part 2

CERTIFICATE OF ANALYSIS

WHI10000694.1

		Method	7TD	7TD	7TD	7TD	G8SG
		Analyte	Na	K	W	S	SG
		Unit	%	%	%	%	
		MDL	0.01	0.01	0.01	0.05	0
633951	Drill Core		0.02	2.16	<0.01	1.55	2.30
633952	Drill Core		<0.01	0.29	<0.01	7.07	2.73
633953	Drill Core		0.02	2.33	<0.01	1.75	2.43
633954	Drill Core		0.01	0.26	<0.01	0.51	2.54
633955	Drill Core		<0.01	0.87	<0.01	1.12	2.41
633956	Drill Core		<0.01	0.96	<0.01	13.04	2.77
633957	Drill Core		<0.01	0.22	<0.01	9.51	2.84
633958	Drill Core		<0.01	0.43	<0.01	12.31	2.92
633959	Drill Core		<0.01	0.11	<0.01	2.11	2.69
633960	Drill Core		<0.01	0.54	<0.01	7.15	2.68
633961	Drill Core		<0.01	0.49	0.01	7.11	2.66
633962	Drill Core		<0.01	0.16	<0.01	3.24	2.61
633963	Drill Core		<0.01	0.17	<0.01	0.94	2.51
633964	Drill Core		<0.01	0.18	<0.01	9.74	2.83
633965	Drill Core		<0.01	0.28	<0.01	3.37	2.65
633966	Drill Core		<0.01	0.43	<0.01	4.06	2.56
633967	Drill Core		<0.01	0.28	<0.01	3.81	2.64
633968	Drill Core		<0.01	0.46	<0.01	1.72	2.62
633969	Drill Core		<0.01	0.23	<0.01	1.46	2.55
633970	Rock		0.04	0.03	<0.01	<0.05	2.70
633971	Drill Core		<0.01	0.19	<0.01	1.06	2.56
633972	Drill Core		<0.01	0.54	<0.01	1.57	2.36
633973	Drill Core		<0.01	0.05	<0.01	0.51	2.54
633974	Drill Core		<0.01	0.65	<0.01	2.16	2.33
633975	Drill Core		<0.01	0.77	<0.01	4.07	2.24
633976	Drill Core		<0.01	1.50	<0.01	3.40	2.13
633977	Drill Core		<0.01	1.31	<0.01	1.65	2.61
633978	Drill Core		<0.01	1.63	<0.01	3.09	2.51
633979	Drill Core		<0.01	2.50	<0.01	3.39	2.22
633980	Rock Pulp		1.70	1.25	<0.01	3.21	N.A.



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: January 07, 2011

Page: 3 of 4 Part 1

CERTIFICATE OF ANALYSIS

WHI10000694.1

	Method Analyte Unit MDL	WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD
		Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg	Al
		kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%	%
		0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01	0.01
633981	Drill Core	0.89	<0.001	0.003	<0.02	0.09	<2	0.005	<0.001	0.01	0.83	<0.02	<0.01	<0.001	<0.01	<0.01	6.17	1.01	0.003	0.12	0.98
633982	Drill Core	0.38	<0.001	0.003	<0.02	0.09	<2	0.004	<0.001	0.01	0.84	<0.02	<0.01	<0.001	<0.01	<0.01	10.79	0.91	0.003	0.12	0.97
633983	Drill Core	0.56	0.003	0.014	1.49	9.02	4	0.010	<0.001	0.03	14.31	<0.02	<0.01	0.028	<0.01	<0.01	9.14	0.04	0.002	0.07	0.72
633984	Drill Core	1.26	0.001	0.001	0.12	0.81	<2	0.003	<0.001	0.09	1.51	<0.02	0.02	0.002	<0.01	<0.01	27.88	0.02	<0.001	0.11	0.22
633985	Drill Core	2.00	0.004	0.006	1.92	9.35	3	0.010	<0.001	0.02	4.11	<0.02	<0.01	0.024	<0.01	<0.01	4.87	0.07	0.002	0.08	0.97
633986	Drill Core	0.72	<0.001	0.001	5.62	0.89	2	0.003	<0.001	0.05	1.24	<0.02	0.01	0.003	<0.01	<0.01	26.01	0.03	<0.001	0.10	0.29
633987	Drill Core	0.99	0.004	0.003	0.30	1.99	<2	0.008	<0.001	<0.01	2.17	<0.02	<0.01	0.007	<0.01	<0.01	1.25	0.04	0.002	0.07	0.92
633988	Drill Core	0.63	0.010	0.003	0.03	0.05	<2	0.014	<0.001	<0.01	1.23	<0.02	<0.01	<0.001	<0.01	<0.01	0.88	0.04	0.003	0.13	2.11
633989	Drill Core	1.04	0.006	0.021	1.53	10.75	3	0.012	<0.001	0.04	13.95	<0.02	<0.01	0.028	<0.01	<0.01	6.30	0.07	0.002	0.07	0.93
633990	Drill Core	1.49	<0.001	<0.001	0.44	0.57	<2	0.001	<0.001	0.06	0.57	<0.02	0.02	0.002	<0.01	<0.01	28.16	0.04	<0.001	0.13	0.24
633991	Drill Core	1.64	0.001	0.002	0.48	1.39	<2	0.003	<0.001	0.07	1.31	<0.02	0.02	0.004	<0.01	<0.01	29.95	0.05	<0.001	0.13	0.28
633992	Drill Core	1.45	0.002	0.003	0.92	4.41	<2	0.006	<0.001	0.03	2.24	<0.02	<0.01	0.011	<0.01	<0.01	8.93	0.08	0.002	0.11	0.93
633993	Drill Core	2.07	0.002	0.002	0.71	3.27	<2	0.004	<0.001	0.04	2.34	<0.02	0.02	0.009	<0.01	<0.01	26.78	0.04	0.002	0.09	0.39
633994	Drill Core	0.90	0.001	0.004	2.26	14.87	4	0.004	<0.001	0.04	2.93	<0.02	0.01	0.035	<0.01	<0.01	23.64	0.03	<0.001	0.07	0.23
633995	Drill Core	1.59	0.002	0.003	2.11	5.78	<2	0.006	<0.001	0.03	2.10	<0.02	<0.01	0.014	<0.01	<0.01	12.29	0.07	0.002	0.09	0.68
633996	Drill Core	2.06	0.002	0.003	0.47	2.49	<2	0.005	<0.001	0.03	1.81	<0.02	0.01	0.006	<0.01	<0.01	17.01	0.06	0.002	0.10	0.70
633997	Drill Core	1.89	0.002	0.004	0.68	5.63	<2	0.006	<0.001	0.02	1.92	<0.02	<0.01	0.015	<0.01	<0.01	4.29	0.05	0.002	0.07	0.59
633998	Drill Core	1.56	0.002	0.002	0.29	1.20	<2	0.005	<0.001	0.04	0.68	<0.02	0.01	0.003	<0.01	<0.01	19.99	0.06	0.002	0.12	0.72
633999	Drill Core	1.43	0.001	0.001	2.34	0.46	<2	0.004	<0.001	0.02	0.55	<0.02	<0.01	0.001	<0.01	<0.01	10.31	0.05	0.002	0.09	0.59
634000	Rock	0.41	<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	0.02	0.16	<0.02	0.01	<0.001	<0.01	<0.01	21.78	0.03	<0.001	11.01	0.14
634651	Drill Core	2.65	0.001	0.004	0.03	0.03	<2	0.005	<0.001	0.04	2.31	<0.02	0.02	<0.001	<0.01	<0.01	28.16	0.04	0.001	0.11	0.54
634652	Drill Core	1.21	0.001	0.004	0.08	0.47	<2	0.004	<0.001	0.02	0.66	<0.02	<0.01	0.001	<0.01	<0.01	8.11	0.04	0.002	0.17	0.54
634653	Drill Core	2.02	0.003	0.013	0.52	1.25	2	0.007	<0.001	0.03	2.33	<0.02	0.01	0.003	<0.01	<0.01	15.79	2.25	0.003	0.09	0.52
634654	Drill Core	1.25	0.004	0.009	0.43	0.36	2	0.006	<0.001	0.05	1.05	<0.02	0.02	0.001	<0.01	<0.01	25.94	0.55	0.002	0.10	0.33
634655	Drill Core	1.80	0.003	0.009	0.13	1.20	<2	0.008	<0.001	0.02	0.54	<0.02	0.01	0.003	<0.01	<0.01	13.27	0.77	0.003	0.08	0.57
634656	Drill Core	1.80	0.005	0.013	0.28	1.88	3	0.012	<0.001	0.02	1.35	<0.02	<0.01	0.004	<0.01	<0.01	10.18	0.30	0.005	0.11	0.91
634657	Drill Core	1.70	0.010	0.014	0.29	1.55	3	0.018	<0.001	<0.01	0.97	<0.02	<0.01	0.004	<0.01	<0.01	2.84	0.25	0.005	0.15	1.31
634658	Drill Core	1.33	0.008	0.014	0.08	0.86	2	0.027	<0.001	<0.01	2.17	<0.02	<0.01	0.003	<0.01	<0.01	5.12	1.61	0.010	0.20	1.76
634659	Drill Core	0.42	0.001	0.003	0.07	0.12	<2	0.066	<0.001	0.02	0.39	<0.02	0.02	<0.001	<0.01	<0.01	16.06	0.82	0.003	0.08	0.60
634660	Rock Pulp	0.06	<0.001	0.663	5.93	6.97	70	<0.001	0.001	0.09	4.79	<0.02	0.02	0.019	0.03	<0.01	1.35	0.02	0.002	0.24	4.73



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: January 07, 2011

Page: 3 of 4 **Part** 2

CERTIFICATE OF ANALYSIS

WHI10000694.1

	Method	7TD	7TD	7TD	7TD	G8SG
	Analyte	Na	K	W	S	SG
	Unit	%	%	%	%	
	MDL	0.01	0.01	0.01	0.05	0
633981	Drill Core	<0.01	0.67	<0.01	0.83	2.46
633982	Drill Core	<0.01	0.71	<0.01	0.85	2.49
633983	Drill Core	<0.01	0.42	<0.01	20.95	2.98
633984	Drill Core	<0.01	0.12	<0.01	2.27	2.73
633985	Drill Core	<0.01	0.61	<0.01	9.48	2.62
633986	Drill Core	<0.01	0.16	<0.01	2.78	2.68
633987	Drill Core	<0.01	0.61	<0.01	3.20	2.39
633988	Drill Core	<0.01	1.64	<0.01	1.40	2.18
633989	Drill Core	<0.01	0.62	<0.01	21.05	2.96
633990	Drill Core	<0.01	0.13	<0.01	1.05	2.60
633991	Drill Core	<0.01	0.16	<0.01	2.16	2.53
633992	Drill Core	<0.01	0.58	<0.01	4.46	2.48
633993	Drill Core	<0.01	0.22	<0.01	4.16	2.54
633994	Drill Core	<0.01	0.12	<0.01	10.22	2.77
633995	Drill Core	<0.01	0.40	<0.01	5.00	2.63
633996	Drill Core	<0.01	0.42	<0.01	3.17	2.54
633997	Drill Core	<0.01	0.33	<0.01	4.40	2.53
633998	Drill Core	<0.01	0.43	<0.01	1.26	2.50
633999	Drill Core	<0.01	0.33	<0.01	0.95	2.46
634000	Rock	<0.01	0.04	<0.01	<0.05	2.78
634651	Drill Core	<0.01	0.29	<0.01	2.46	2.56
634652	Drill Core	<0.01	0.30	<0.01	0.80	2.44
634653	Drill Core	<0.01	0.29	<0.01	2.98	2.54
634654	Drill Core	<0.01	0.18	<0.01	1.32	2.52
634655	Drill Core	<0.01	0.32	<0.01	1.00	2.43
634656	Drill Core	<0.01	0.54	<0.01	2.22	2.36
634657	Drill Core	<0.01	0.79	<0.01	1.66	2.25
634658	Drill Core	<0.01	1.07	<0.01	2.63	2.12
634659	Drill Core	<0.01	0.37	<0.01	0.49	1.66
634660	Rock Pulp	2.33	1.36	<0.01	4.86	N.A.



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: January 07, 2011

Page: 4 of 4 **Part** 1

CERTIFICATE OF ANALYSIS

WHI10000694.1

	Method Analyte Unit MDL	WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD
		Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg
		kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%
		0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01
634661	Drill Core	0.48	0.001	0.008	0.19	0.32	2	0.025	<0.001	0.01	1.27	<0.02	0.01	<0.001	<0.01	<0.01	10.94	2.75	0.014	0.22
634662	Drill Core	2.97	<0.001	0.002	0.05	<0.01	<2	0.003	<0.001	0.04	1.94	<0.02	0.02	<0.001	<0.01	<0.01	26.67	0.03	0.003	0.35
634663	Drill Core	1.01	0.006	0.008	0.05	0.06	2	0.021	0.001	0.01	3.09	<0.02	0.02	<0.001	<0.01	<0.01	13.86	3.61	0.011	0.32
634664	Drill Core	1.22	0.008	0.013	0.06	0.80	3	0.030	0.001	0.01	3.12	<0.02	<0.01	0.004	<0.01	<0.01	3.26	0.16	0.014	0.39



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**

Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: January 07, 2011

Page: 4 of 4 Part 2

CERTIFICATE OF ANALYSIS

WHI10000694.1

	Method	7TD	7TD	7TD	7TD	G8SG
	Analyte	Na	K	W	S	SG
	Unit	%	%	%	%	
	MDL	0.01	0.01	0.01	0.05	0
634661	Drill Core	<0.01	1.39	<0.01	1.47	2.14
634662	Drill Core	<0.01	1.56	<0.01	2.02	2.58
634663	Drill Core	0.02	2.18	<0.01	3.25	2.28
634664	Drill Core	<0.01	2.75	<0.01	3.54	2.10



Acme Analytical Laboratories (Vancouver) Ltd.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: **Selwyn Resources Ltd.**

Suite 700 - 509 Richards Street

Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: January 07, 2011

Page: 1 of 1 Part 1

QUALITY CONTROL REPORT

WHI10000694.1

	Method Analyte Unit MDL	WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD
		Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg	Al
		kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%	%
		0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01	0.01
Pulp Duplicates																					
633990	Drill Core	1.49	<0.001	<0.001	0.44	0.57	<2	0.001	<0.001	0.06	0.57	<0.02	0.02	0.002	<0.01	<0.01	28.16	0.04	<0.001	0.13	0.24
REP 633990	QC		<0.001	<0.001	0.47	0.61	<2	0.002	<0.001	0.07	0.61	<0.02	0.02	0.001	<0.01	<0.01	29.53	0.04	<0.001	0.13	0.25
634652	Drill Core	1.21	0.001	0.004	0.08	0.47	<2	0.004	<0.001	0.02	0.66	<0.02	<0.01	0.001	<0.01	<0.01	8.11	0.04	0.002	0.17	0.54
REP 634652	QC		0.001	0.004	0.08	0.47	<2	0.004	<0.001	0.02	0.68	<0.02	<0.01	0.001	<0.01	<0.01	8.28	0.04	0.002	0.18	0.55
Core Reject Duplicates																					
633979	Drill Core	2.44	0.007	0.012	0.02	0.23	<2	0.028	<0.001	0.01	3.02	<0.02	<0.01	<0.001	<0.01	<0.01	5.87	0.20	0.016	0.41	3.95
DUP 633979	QC		0.007	0.013	0.03	0.23	3	0.027	<0.001	0.01	3.05	<0.02	<0.01	<0.001	<0.01	<0.01	6.29	0.22	0.017	0.41	3.93
634664	Drill Core	1.22	0.008	0.013	0.06	0.80	3	0.030	0.001	0.01	3.12	<0.02	<0.01	0.004	<0.01	<0.01	3.26	0.16	0.014	0.39	3.98
DUP 634664	QC		0.008	0.013	0.07	0.78	3	0.030	0.001	0.01	3.13	<0.02	<0.01	0.004	<0.01	<0.01	3.48	0.17	0.015	0.38	3.95
Reference Materials																					
STD OREAS131A	Standard		<0.001	0.032	1.71	2.87	30	0.002	0.002	0.17	5.91	<0.02	<0.01	0.008	<0.01	<0.01	5.34	0.06	0.002	3.15	4.63
STD OREAS131A	Standard		<0.001	0.032	1.68	2.89	31	0.003	0.002	0.17	5.87	<0.02	<0.01	0.008	<0.01	<0.01	5.44	0.06	0.003	3.14	4.57
STD OREAS131A	Standard		<0.001	0.032	1.71	2.89	31	0.003	0.002	0.18	5.89	<0.02	<0.01	0.008	<0.01	<0.01	5.42	0.06	0.002	3.17	4.58
STD R4T	Standard		0.064	0.511	1.57	3.45	86	0.355	0.041	0.09	24.63	<0.02	0.02	0.019	0.02	<0.01	2.20	0.04	0.019	1.42	3.98
STD R4T	Standard		0.064	0.515	1.52	3.48	89	0.355	0.041	0.09	24.65	<0.02	0.02	0.019	0.02	<0.01	2.20	0.05	0.017	1.41	3.95
STD R4T	Standard		0.066	0.524	1.59	3.54	90	0.361	0.043	0.09	25.08	<0.02	0.02	0.019	0.01	<0.01	2.24	0.05	0.019	1.45	4.02
STD SU-1B	Standard		<0.001	1.164	<0.02	0.02	9	1.976	0.067	0.07	25.50	<0.02	0.03	0.002	<0.01	<0.01	2.19	0.06	0.030	1.76	4.35
STD SU-1B	Standard		<0.001	1.211	<0.02	0.02	7	2.012	0.068	0.07	25.96	<0.02	0.03	<0.001	<0.01	<0.01	2.24	0.07	0.030	1.80	4.37
STD SU-1B	Standard		<0.001	1.193	<0.02	0.03	7	2.024	0.068	0.07	26.19	<0.02	0.03	<0.001	<0.01	<0.01	2.24	0.06	0.033	1.80	4.38
STD R4T Expected			0.062	0.502	1.518	3.376	86	0.339	0.039	0.086	24.07	0.0087	0.0185	0.018	0.0138	0.0018	2.166	0.045	0.018	1.384	3.897
STD OREAS131A Expected			0.001	0.0322	1.72	2.83	30.9	0.0027	0.0023	0.1722	5.8166	0.0082	0.0028	0.0081	0.0047	0.001	5.286	0.0536	0.0025	3.1182	4.6057
STD SU-1B Expected			0.0004	1.185	0.0058	0.0235	6.4	1.97	0.0672	0.0703	25.54	0.00025	0.03	0.0003	0.00002	0.0003	2.21	0.06	0.032	1.79	4.39
BLK	Blank		<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	<0.01	<0.01	<0.02	<0.01	<0.001	<0.01	<0.01	<0.01	<0.01	<0.001	<0.01	<0.01
BLK	Blank		<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	<0.01	<0.01	<0.02	<0.01	<0.001	<0.01	<0.01	<0.01	<0.01	<0.001	<0.01	<0.01
BLK	Blank		<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	<0.01	<0.01	<0.02	<0.01	<0.001	<0.01	<0.01	<0.01	<0.01	<0.001	<0.01	<0.01
Prep Wash																					
G1	Prep Blank		<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	0.07	2.36	<0.02	0.07	<0.001	<0.01	<0.01	2.36	0.07	0.003	0.60	7.05
G1	Prep Blank		<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	0.08	2.52	<0.02	0.07	<0.001	<0.01	<0.01	2.39	0.08	0.002	0.63	7.19



Acme Analytical Laboratories (Vancouver) Ltd.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: **Selwyn Resources Ltd.**

Suite 700 - 509 Richards Street

Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: January 07, 2011

Page: 1 of 1 Part 2

QUALITY CONTROL REPORT

WHI10000694.1

Method		7TD	7TD	7TD	7TD	G8SG
Analyte		Na	K	W	S	SG
Unit		%	%	%	%	%
MDL		0.01	0.01	0.01	0.05	0
Pulp Duplicates						
633990	Drill Core	<0.01	0.13	<0.01	1.05	2.60
REP 633990	QC	<0.01	0.14	<0.01	1.09	
634652	Drill Core	<0.01	0.30	<0.01	0.80	2.44
REP 634652	QC	<0.01	0.31	<0.01	0.82	
Core Reject Duplicates						
633979	Drill Core	<0.01	2.50	<0.01	3.39	2.22
DUP 633979	QC	<0.01	2.49	<0.01	3.43	2.18
634664	Drill Core	<0.01	2.75	<0.01	3.54	2.10
DUP 634664	QC	<0.01	2.72	<0.01	3.57	2.08
Reference Materials						
STD OREAS131A	Standard	0.15	3.40	<0.01	4.79	
STD OREAS131A	Standard	0.15	3.46	<0.01	4.40	
STD OREAS131A	Standard	0.15	3.50	<0.01	4.40	
STD R4T	Standard	0.92	1.19	<0.01	11.90	
STD R4T	Standard	0.94	1.19	<0.01	12.86	
STD R4T	Standard	0.95	1.22	<0.01	11.72	
STD SU-1B	Standard	1.67	0.61	<0.01	8.71	
STD SU-1B	Standard	1.72	0.63	<0.01	9.19	
STD SU-1B	Standard	1.72	0.63	<0.01	7.91	
STD R4T Expected		0.9	1.153	0.00016	12.9903	
STD OREAS131A Expected		0.1501	3.1584	0.0005	4.8	
STD SU-1B Expected		1.662	0.6	0.0007	8.76	
BLK	Blank	<0.01	<0.01	<0.01	<0.05	
BLK	Blank	<0.01	<0.01	<0.01	<0.05	
BLK	Blank	<0.01	<0.01	<0.01	<0.05	
Prep Wash						
G1	Prep Blank	2.69	3.07	<0.01	<0.05	2.67
G1	Prep Blank	2.66	3.10	<0.01	<0.05	2.75



1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: Selwyn Resources Ltd.

Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Submitted By: Jason K. Dunning

Receiving Lab: Canada-Whitehorse

Received: December 16, 2010

Report Date: January 06, 2011

Page: 1 of 3

CERTIFICATE OF ANALYSIS

WHI10000693.1

CLIENT JOB INFORMATION

Project: Selwyn Project
Shipment ID:
P.O. Number 1163
Number of Samples: 50

SAMPLE DISPOSAL

STOR-PLP Store After 90 days Invoice for Storage
STOR-RJT Store After 90 days Invoice for Storage

Acme does not accept responsibility for samples left at the laboratory after 90 days without prior written instructions for sample storage or return.

Invoice To: Selwyn Resources Ltd.
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6
Canada

CC:

SAMPLE PREPARATION AND ANALYTICAL PROCEDURES

Method Code	Number of Samples	Code Description	Test Wgt (g)	Report Status	Lab
R200-250	49	Crush split and pulverize 250g drill core to 200 mesh			WHI
7TD2	50	4 Acid digestion ICP-ES analysis.	0.5	Completed	VAN
G812	50	Specific Gravity on Pulp		Completed	VAN

ADDITIONAL COMMENTS



This report supersedes all previous preliminary and final reports with this file number dated prior to the date on this certificate. Signature indicates final approval; preliminary reports are unsigned and should be used for reference only.
All results are considered the confidential property of the client. Acme assumes the liabilities for actual cost of analysis only.
** asterisk indicates that an analytical result could not be provided due to unusually high levels of interference from other elements.



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: January 06, 2011

Page: 2 of 3 Part 1

CERTIFICATE OF ANALYSIS

WHI10000693.1

	Method Analyte Unit MDL	WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD
		Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg	Al
		kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%	%
		0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01	0.01
634001	Drill Core	1.46	<0.001	0.010	0.02	0.09	<2	0.008	<0.001	<0.01	2.38	<0.02	<0.01	<0.001	<0.01	<0.01	3.25	0.63	0.004	0.12	1.15
634002	Drill Core	0.97	0.003	0.003	0.02	0.36	<2	0.008	<0.001	<0.01	1.42	<0.02	<0.01	0.001	<0.01	<0.01	2.64	0.77	0.004	0.12	1.24
634003	Drill Core	0.84	0.002	0.008	2.04	7.23	3	0.006	<0.001	0.01	8.52	<0.02	<0.01	0.028	<0.01	<0.01	0.94	0.04	0.003	0.06	0.58
634004	Drill Core	1.05	0.003	0.007	0.74	3.50	2	0.008	<0.001	0.02	7.71	<0.02	<0.01	0.010	<0.01	<0.01	2.82	0.03	0.003	0.07	0.75
634005	Drill Core	0.74	0.004	0.007	2.05	6.20	3	0.010	<0.001	0.03	5.61	<0.02	<0.01	0.018	<0.01	<0.01	6.67	0.08	0.003	0.12	1.11
634006	Drill Core	0.99	0.005	0.010	0.95	10.92	3	0.010	<0.001	0.02	7.82	<0.02	<0.01	0.028	<0.01	<0.01	5.23	0.07	0.002	0.10	1.11
634007	Drill Core	0.90	0.002	0.003	1.60	3.00	<2	0.005	<0.001	0.02	2.79	<0.02	<0.01	0.009	<0.01	<0.01	5.91	0.04	0.002	0.06	0.55
634008	Drill Core	1.32	0.001	0.001	0.08	0.53	<2	0.003	<0.001	0.01	0.52	<0.02	<0.01	0.001	<0.01	<0.01	4.39	0.03	0.002	0.04	0.28
634009	Drill Core	1.22	0.001	0.002	0.21	1.39	<2	0.005	<0.001	<0.01	1.18	<0.02	<0.01	0.004	<0.01	<0.01	1.26	0.04	0.003	0.05	0.44
634010	Drill Core	0.60	0.005	0.002	0.03	0.10	<2	0.009	<0.001	0.02	1.26	<0.02	<0.01	<0.001	<0.01	<0.01	8.60	0.04	0.003	0.11	1.18
634011	Drill Core	0.74	0.005	0.002	0.03	0.10	<2	0.009	<0.001	0.01	1.60	<0.02	<0.01	<0.001	<0.01	<0.01	5.94	0.04	0.003	0.11	1.25
634012	Drill Core	0.88	0.005	0.012	1.73	8.19	3	0.011	<0.001	0.04	9.86	<0.02	<0.01	0.026	<0.01	<0.01	6.75	0.05	0.002	0.08	0.94
634013	Drill Core	1.07	0.002	0.009	5.19	19.14	4	0.005	<0.001	0.02	5.50	<0.02	<0.01	0.075	<0.01	<0.01	5.80	0.04	0.001	0.04	0.35
634014	Drill Core	1.63	<0.001	<0.001	0.79	0.47	<2	0.002	<0.001	0.08	0.81	<0.02	0.02	0.002	<0.01	<0.01	30.78	0.05	<0.001	0.11	0.09
634015	Drill Core	0.57	<0.001	0.002	1.00	1.86	<2	0.004	<0.001	0.02	1.32	<0.02	<0.01	0.005	<0.01	<0.01	9.14	0.05	0.001	0.06	0.31
634016	Drill Core	0.91	<0.001	0.002	0.75	2.84	<2	0.006	<0.001	0.02	1.59	<0.02	<0.01	0.008	<0.01	<0.01	6.39	0.07	0.001	0.08	0.51
634017	Drill Core	0.99	<0.001	0.002	0.68	2.46	<2	0.006	<0.001	0.01	1.73	<0.02	<0.01	0.007	<0.01	<0.01	2.34	0.06	0.002	0.09	0.66
634018	Drill Core	0.71	<0.001	0.003	0.96	4.39	<2	0.005	<0.001	0.03	2.36	<0.02	<0.01	0.012	<0.01	<0.01	6.50	0.07	0.002	0.10	0.72
634019	Drill Core	0.82	0.001	0.002	1.14	3.13	<2	0.003	<0.001	0.05	2.22	<0.02	0.02	0.009	<0.01	<0.01	27.93	0.03	<0.001	0.07	0.24
634020	Rock	0.41	<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	0.03	0.19	<0.02	0.01	<0.001	<0.01	<0.01	21.30	0.03	<0.001	10.88	0.13
634021	Drill Core	1.34	0.002	0.003	0.89	4.37	<2	0.003	<0.001	0.05	2.36	<0.02	0.02	0.012	<0.01	<0.01	27.32	0.03	<0.001	0.09	0.30
634022	Drill Core	0.97	<0.001	0.002	1.31	5.52	3	0.002	<0.001	0.05	1.10	<0.02	0.02	0.019	<0.01	<0.01	29.33	0.03	<0.001	0.08	0.13
634023	Drill Core	0.84	0.001	0.004	1.32	1.69	2	0.006	<0.001	0.03	11.14	<0.02	0.01	0.005	<0.01	<0.01	12.50	0.07	0.002	0.12	0.73
634024	Drill Core	1.65	0.002	0.003	4.24	1.63	3	0.009	<0.001	0.03	2.81	<0.02	<0.01	0.004	<0.01	<0.01	9.83	0.07	0.003	0.13	0.93
634025	Drill Core	1.58	0.002	0.005	6.10	33.09	6	0.004	<0.001	0.01	1.49	<0.02	<0.01	0.097	<0.01	<0.01	0.45	0.03	0.005	0.03	0.24
634026	Drill Core	1.51	0.001	0.004	8.98	26.53	6	0.004	<0.001	<0.01	1.28	<0.02	<0.01	0.085	<0.01	<0.01	0.49	0.04	0.005	0.03	0.25
634027	Drill Core	1.35	0.001	0.005	6.60	23.65	6	0.005	<0.001	<0.01	2.26	<0.02	<0.01	0.070	<0.01	<0.01	0.71	0.04	0.003	0.04	0.32
634028	Drill Core	0.79	0.005	0.008	2.66	6.59	5	0.014	<0.001	0.03	8.96	<0.02	<0.01	0.019	<0.01	<0.01	8.79	0.06	0.004	0.12	1.00
634029	Drill Core	1.56	0.004	0.004	0.99	4.50	<2	0.010	<0.001	0.02	3.52	<0.02	<0.01	0.013	<0.01	<0.01	6.33	0.07	0.003	0.13	1.07
634030	Rock Pulp	0.06	<0.001	0.659	5.82	6.91	68	<0.001	0.001	0.09	4.90	<0.02	0.02	0.019	0.02	<0.01	1.34	0.02	0.003	0.24	5.00



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**

Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: January 06, 2011

Page: 2 of 3 **Part** 2

CERTIFICATE OF ANALYSIS

WHI10000693.1

	Method	7TD	7TD	7TD	7TD	G8SG
	Analyte	Na	K	W	S	SG
	Unit	%	%	%	%	
	MDL	0.01	0.01	0.01	0.05	0
634001	Drill Core	<0.01	0.74	<0.01	2.67	2.43
634002	Drill Core	<0.01	0.83	<0.01	1.63	2.36
634003	Drill Core	<0.01	0.35	<0.01	13.88	2.78
634004	Drill Core	<0.01	0.52	<0.01	10.96	2.64
634005	Drill Core	<0.01	0.70	<0.01	10.14	2.58
634006	Drill Core	<0.01	0.73	<0.01	14.98	2.68
634007	Drill Core	<0.01	0.35	<0.01	4.98	2.54
634008	Drill Core	<0.01	0.15	<0.01	0.66	2.42
634009	Drill Core	<0.01	0.27	<0.01	1.68	2.43
634010	Drill Core	<0.01	0.86	<0.01	1.44	2.31
634011	Drill Core	<0.01	0.93	<0.01	1.76	2.29
634012	Drill Core	<0.01	0.77	<0.01	16.02	2.81
634013	Drill Core	<0.01	0.24	<0.01	16.69	2.97
634014	Drill Core	<0.01	0.08	<0.01	1.30	2.51
634015	Drill Core	<0.01	0.18	<0.01	2.43	2.50
634016	Drill Core	<0.01	0.30	<0.01	3.26	2.43
634017	Drill Core	<0.01	0.40	<0.01	3.15	2.44
634018	Drill Core	<0.01	0.47	<0.01	4.84	2.50
634019	Drill Core	<0.01	0.18	<0.01	4.36	2.56
634020	Rock	<0.01	0.03	<0.01	<0.05	2.63
634021	Drill Core	<0.01	0.20	<0.01	5.10	2.62
634022	Drill Core	<0.01	0.10	<0.01	4.26	2.61
634023	Drill Core	<0.01	0.49	<0.01	14.41	2.80
634024	Drill Core	<0.01	0.58	<0.01	4.63	2.47
634025	Drill Core	<0.01	0.13	<0.01	16.84	3.06
634026	Drill Core	<0.01	0.14	<0.01	14.07	3.00
634027	Drill Core	<0.01	0.19	<0.01	13.61	2.90
634028	Drill Core	<0.01	0.60	<0.01	12.97	2.65
634029	Drill Core	<0.01	0.62	<0.01	5.80	2.43
634030	Rock Pulp	2.31	1.32	<0.01	5.35	N.A.



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: Selwyn Resources Ltd.
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: January 06, 2011

Page: 3 of 3 **Part** 1

CERTIFICATE OF ANALYSIS

WHI10000693.1

	Method Analyte Unit MDL	WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	
		Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg	Al
		kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%	%
		0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01	0.01
634031	Drill Core	0.94	0.002	0.004	0.44	5.18	<2	0.009	<0.001	0.02	2.03	<0.02	<0.01	0.014	<0.01	<0.01	5.01	0.08	0.004	0.11	0.80
634032	Drill Core	0.51	0.003	0.006	0.46	8.06	<2	0.010	<0.001	0.01	2.30	<0.02	<0.01	0.022	<0.01	<0.01	3.51	0.10	0.002	0.13	1.03
634033	Drill Core	2.76	0.001	0.001	0.69	0.37	<2	0.004	<0.001	0.04	0.67	<0.02	0.02	0.002	<0.01	<0.01	26.91	0.05	0.003	0.13	0.62
634034	Drill Core	1.80	<0.001	<0.001	0.02	0.07	<2	0.004	<0.001	0.01	0.35	<0.02	<0.01	<0.001	<0.01	<0.01	8.66	0.04	0.002	0.08	0.59
634035	Drill Core	1.47	0.002	0.001	<0.02	0.07	<2	0.007	<0.001	0.01	0.51	<0.02	<0.01	<0.001	<0.01	<0.01	7.62	0.08	0.002	0.12	0.91
634036	Drill Core	0.79	<0.001	0.003	<0.02	<0.01	<2	0.006	<0.001	<0.01	1.20	<0.02	<0.01	<0.001	<0.01	<0.01	3.34	0.06	0.003	0.09	0.65
634037	Drill Core	0.82	0.001	0.011	0.10	<0.01	<2	0.009	<0.001	0.02	7.68	<0.02	<0.01	<0.001	<0.01	<0.01	9.61	0.05	0.003	0.09	0.60
634038	Drill Core	1.06	0.002	0.004	<0.02	<0.01	<2	0.005	<0.001	0.04	0.57	<0.02	0.02	<0.001	<0.01	<0.01	25.27	0.08	0.002	0.13	0.83
634039	Drill Core	1.64	0.002	0.008	0.11	<0.01	<2	0.009	<0.001	0.04	8.54	<0.02	0.01	<0.001	<0.01	<0.01	19.33	0.06	0.002	0.12	0.80
634040	Drill Core	0.37	<0.001	0.001	<0.02	<0.01	<2	0.002	<0.001	0.04	0.88	<0.02	0.02	<0.001	<0.01	<0.01	33.08	0.02	<0.001	0.08	0.21
634041	Drill Core	0.40	<0.001	0.001	<0.02	<0.01	<2	0.003	<0.001	0.04	0.96	<0.02	0.02	<0.001	<0.01	<0.01	33.88	0.02	0.002	0.08	0.22
634042	Drill Core	0.98	0.001	0.004	1.16	<0.01	3	0.006	<0.001	0.04	3.43	<0.02	0.01	<0.001	<0.01	<0.01	21.03	0.04	0.003	0.10	0.57
634043	Drill Core	1.25	0.002	0.009	0.09	<0.01	<2	0.009	<0.001	0.02	7.07	<0.02	<0.01	<0.001	<0.01	<0.01	9.04	0.05	0.003	0.12	0.91
634044	Drill Core	1.13	0.001	0.004	0.04	0.02	<2	0.005	<0.001	<0.01	0.69	<0.02	<0.01	<0.001	<0.01	<0.01	3.50	0.03	0.003	0.07	0.50
634045	Drill Core	0.42	0.002	0.002	0.07	0.67	<2	0.005	<0.001	0.02	1.17	<0.02	<0.01	0.002	<0.01	<0.01	10.77	0.10	0.002	0.07	0.40
634046	Drill Core	1.40	0.005	0.006	0.65	0.83	3	0.010	<0.001	0.02	1.26	<0.02	0.01	0.003	<0.01	<0.01	12.47	0.75	0.004	0.14	1.05
634047	Drill Core	1.80	<0.001	0.003	0.04	<0.01	<2	0.003	<0.001	0.04	2.31	<0.02	0.01	<0.001	<0.01	<0.01	23.59	0.08	0.004	0.37	2.71
634048	Drill Core	1.25	0.003	0.005	0.04	0.07	<2	0.012	<0.001	0.03	1.97	<0.02	0.02	<0.001	<0.01	<0.01	17.46	1.55	0.007	0.36	3.14
634049	Drill Core	0.91	0.008	0.009	0.19	1.29	2	0.033	0.001	<0.01	3.49	<0.02	<0.01	0.008	<0.01	<0.01	2.04	0.23	0.015	0.49	4.45
634050	Rock	0.32	<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	0.02	0.17	<0.02	<0.01	<0.001	<0.01	<0.01	21.23	0.03	<0.001	11.14	0.14



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**

Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: January 06, 2011

Page: 3 of 3 **Part** 2

CERTIFICATE OF ANALYSIS

WHI10000693.1

	Method	7TD	7TD	7TD	7TD	G8SG
	Analyte	Na	K	W	S	SG
	Unit	%	%	%	%	
	MDL	0.01	0.01	0.01	0.05	0
634031	Drill Core	<0.01	0.45	<0.01	4.26	2.41
634032	Drill Core	<0.01	0.59	<0.01	5.82	2.43
634033	Drill Core	<0.01	0.35	<0.01	0.88	2.48
634034	Drill Core	<0.01	0.34	<0.01	0.25	2.39
634035	Drill Core	<0.01	0.54	<0.01	0.40	2.34
634036	Drill Core	<0.01	0.37	<0.01	1.01	2.32
634037	Drill Core	<0.01	0.35	<0.01	8.18	2.63
634038	Drill Core	<0.01	0.46	<0.01	0.55	2.43
634039	Drill Core	<0.01	0.44	<0.01	9.09	2.69
634040	Drill Core	<0.01	0.12	<0.01	0.95	2.50
634041	Drill Core	<0.01	0.12	<0.01	1.01	2.55
634042	Drill Core	<0.01	0.33	<0.01	3.73	2.56
634043	Drill Core	<0.01	0.56	<0.01	7.64	2.56
634044	Drill Core	<0.01	0.29	<0.01	0.57	2.41
634045	Drill Core	<0.01	0.23	<0.01	1.27	2.47
634046	Drill Core	<0.01	0.64	<0.01	1.68	2.29
634047	Drill Core	<0.01	1.61	<0.01	2.42	2.54
634048	Drill Core	<0.01	1.98	<0.01	1.94	2.38
634049	Drill Core	<0.01	2.86	<0.01	4.08	1.99
634050	Rock	<0.01	0.03	<0.01	<0.05	2.59



Acme Analytical Laboratories (Vancouver) Ltd.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: **Selwyn Resources Ltd.**

Suite 700 - 509 Richards Street

Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: January 06, 2011

Page: 1 of 1 Part 1

QUALITY CONTROL REPORT

WHI10000693.1

	Method Analyte Unit MDL	WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD
		Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg	Al
		kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%	%
		0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01	0.01
Pulp Duplicates																					
634029	Drill Core	1.56	0.004	0.004	0.99	4.50	<2	0.010	<0.001	0.02	3.52	<0.02	<0.01	0.013	<0.01	<0.01	6.33	0.07	0.003	0.13	1.07
REP 634029	QC		0.004	0.004	0.97	4.48	2	0.010	<0.001	0.02	3.51	<0.02	<0.01	0.013	<0.01	<0.01	6.24	0.07	0.003	0.13	1.06
Core Reject Duplicates																					
634024	Drill Core	1.65	0.002	0.003	4.24	1.63	3	0.009	<0.001	0.03	2.81	<0.02	<0.01	0.004	<0.01	<0.01	9.83	0.07	0.003	0.13	0.93
DUP 634024	QC		0.003	0.003	4.11	1.68	2	0.008	<0.001	0.03	2.69	<0.02	<0.01	0.005	<0.01	<0.01	9.88	0.07	0.004	0.12	0.97
Reference Materials																					
STD OREAS131A	Standard		<0.001	0.032	1.77	2.92	32	0.003	0.002	0.17	5.87	<0.02	<0.01	0.008	<0.01	<0.01	5.42	0.06	0.002	3.17	4.68
STD OREAS131A	Standard		<0.001	0.032	1.68	2.89	31	0.003	0.002	0.17	5.87	<0.02	<0.01	0.008	<0.01	<0.01	5.44	0.06	0.003	3.14	4.57
STD R4T	Standard		0.064	0.502	1.55	3.45	87	0.352	0.040	0.09	23.98	<0.02	0.02	0.019	0.02	<0.01	2.18	0.04	0.018	1.41	3.94
STD R4T	Standard		0.064	0.515	1.52	3.48	89	0.355	0.041	0.09	24.65	<0.02	0.02	0.019	0.02	<0.01	2.20	0.05	0.017	1.41	3.95
STD SU-1B	Standard		<0.001	1.190	<0.02	0.03	7	1.984	0.067	0.07	25.32	<0.02	0.03	<0.001	<0.01	<0.01	2.24	0.06	0.031	1.80	4.43
STD SU-1B	Standard		<0.001	1.211	<0.02	0.02	7	2.012	0.068	0.07	25.96	<0.02	0.03	<0.001	<0.01	<0.01	2.24	0.07	0.030	1.80	4.37
STD R4T Expected			0.062	0.502	1.518	3.376	86	0.339	0.039	0.086	24.07	0.0087	0.0185	0.018	0.0138	0.0018	2.166	0.045	0.018	1.384	3.897
STD OREAS131A Expected			0.001	0.0322	1.72	2.83	30.9	0.0027	0.0023	0.1722	5.8166	0.0082	0.0028	0.0081	0.0047	0.001	5.286	0.0536	0.0025	3.1182	4.6057
STD SU-1B Expected			0.0004	1.185	0.0058	0.0235	6.4	1.97	0.0672	0.0703	25.54	0.00025	0.03	0.0003	0.00002	0.0003	2.21	0.06	0.032	1.79	4.39
BLK	Blank		<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	<0.01	<0.01	<0.02	<0.01	<0.001	<0.01	<0.01	<0.01	<0.01	<0.001	<0.01	<0.01
BLK	Blank		<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	<0.01	<0.01	<0.02	<0.01	<0.001	<0.01	<0.01	<0.01	<0.01	<0.001	<0.01	<0.01
Prep Wash																					
G1	Prep Blank		<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	0.07	2.36	<0.02	0.07	<0.001	<0.01	<0.01	2.35	0.08	0.001	0.64	7.43
G1	Prep Blank		<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	0.07	2.36	<0.02	0.07	<0.001	<0.01	<0.01	2.29	0.07	0.001	0.60	7.41



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**

Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: January 06, 2011

Page: 1 of 1 **Part** 2

QUALITY CONTROL REPORT

WHI10000693.1

Method		7TD	7TD	7TD	7TD	G8SG
Analyte		Na	K	W	S	SG
Unit		%	%	%	%	%
MDL		0.01	0.01	0.01	0.05	0
Pulp Duplicates						
634029	Drill Core	<0.01	0.62	<0.01	5.80	2.43
REP 634029	QC	<0.01	0.60	<0.01	5.73	
Core Reject Duplicates						
634024	Drill Core	<0.01	0.58	<0.01	4.63	2.47
DUP 634024	QC	<0.01	0.59	<0.01	4.23	2.53
Reference Materials						
STD OREAS131A	Standard	0.16	3.43	<0.01	5.01	
STD OREAS131A	Standard	0.15	3.46	<0.01	4.40	
STD R4T	Standard	0.91	1.17	<0.01	12.82	
STD R4T	Standard	0.94	1.19	<0.01	12.86	
STD SU-1B	Standard	1.70	0.62	<0.01	9.13	
STD SU-1B	Standard	1.72	0.63	<0.01	9.19	
STD R4T Expected		0.9	1.153	0.00016	12.9903	
STD OREAS131A Expected		0.1501	3.1584	0.0005	4.8	
STD SU-1B Expected		1.662	0.6	0.0007	8.76	
BLK	Blank	<0.01	<0.01	<0.01	<0.05	
BLK	Blank	<0.01	<0.01	<0.01	<0.05	
Prep Wash						
G1	Prep Blank	2.68	3.09	<0.01	<0.05	2.71
G1	Prep Blank	2.63	2.96	<0.01	<0.05	2.72



1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: Selwyn Resources Ltd.

Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Submitted By: Jason K. Dunning

Receiving Lab: Canada-Whitehorse

Received: December 16, 2010

Report Date: January 13, 2011

Page: 1 of 3

CERTIFICATE OF ANALYSIS

WHI10000692.1

CLIENT JOB INFORMATION

Project: Selwyn Project
Shipment ID:
P.O. Number 1163
Number of Samples: 41

SAMPLE DISPOSAL

STOR-PLP Store After 90 days Invoice for Storage
STOR-RJT Store After 90 days Invoice for Storage

Acme does not accept responsibility for samples left at the laboratory after 90 days without prior written instructions for sample storage or return.

Invoice To: Selwyn Resources Ltd.
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6
Canada

CC:

SAMPLE PREPARATION AND ANALYTICAL PROCEDURES

Method Code	Number of Samples	Code Description	Test Wgt (g)	Report Status	Lab
R200-250	40	Crush split and pulverize 250g drill core to 200 mesh			WHI
7TD2	41	4 Acid digestion ICP-ES analysis.	0.5	Completed	VAN
G812	41	Specific Gravity on Pulp		Completed	VAN
7TD.1	2	4 Acid digestion ICP-ES analysis	0.1	Completed	VAN

ADDITIONAL COMMENTS



This report supersedes all previous preliminary and final reports with this file number dated prior to the date on this certificate. Signature indicates final approval; preliminary reports are unsigned and should be used for reference only.
All results are considered the confidential property of the client. Acme assumes the liabilities for actual cost of analysis only.
** asterisk indicates that an analytical result could not be provided due to unusually high levels of interference from other elements.



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: January 13, 2011

Page: 2 of 3 Part 1

CERTIFICATE OF ANALYSIS

WHI10000692.1

Method Analyte Unit MDL		WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD
		Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg	Al
		kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%	%
		0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01	0.01
635101	Drill Core	1.81	0.001	0.003	0.32	0.16	2	0.007	<0.001	0.01	0.90	<0.02	<0.01	<0.001	<0.01	<0.01	4.04	0.91	0.005	0.15	1.38
635102	Drill Core	1.16	<0.001	0.001	<0.02	<0.01	<2	0.002	<0.001	0.11	0.46	<0.02	0.02	<0.001	<0.01	<0.01	34.29	0.05	<0.001	0.16	0.22
635103	Drill Core	1.77	0.003	0.004	0.20	0.61	2	0.010	<0.001	<0.01	0.94	<0.02	<0.01	0.002	<0.01	<0.01	2.05	0.39	0.005	0.15	1.52
635104	Drill Core	0.80	0.004	0.009	1.88	7.58	3	0.007	<0.001	0.01	4.60	<0.02	<0.01	0.033	<0.01	<0.01	0.66	0.03	0.003	0.07	0.87
635105	Drill Core	1.28	0.004	0.008	1.56	5.94	3	0.011	<0.001	0.02	5.39	<0.02	<0.01	0.020	<0.01	<0.01	4.61	0.06	0.004	0.12	1.56
635106	Drill Core	0.74	0.004	0.012	3.13	12.40	5	0.010	<0.001	0.01	10.82	<0.02	<0.01	0.044	<0.01	<0.01	0.28	0.06	0.004	0.10	1.25
635107	Drill Core	1.22	0.001	0.006	5.96	15.77	4	0.005	<0.001	<0.01	5.06	<0.02	<0.01	0.054	<0.01	<0.01	0.34	0.03	0.002	0.04	0.54
635108	Drill Core	1.01	0.005	0.007	1.57	7.50	3	0.011	<0.001	0.02	6.70	<0.02	<0.01	0.020	<0.01	<0.01	1.32	0.06	0.003	0.10	1.26
635109	Drill Core	1.07	0.003	0.004	0.55	4.50	<2	0.005	<0.001	0.06	4.22	<0.02	0.01	0.010	<0.01	<0.01	17.65	0.05	0.001	0.11	0.74
635110	Drill Core	0.61	<0.001	0.001	0.11	0.86	<2	0.003	<0.001	0.06	1.12	<0.02	0.02	0.002	<0.01	<0.01	22.94	0.06	<0.001	0.09	0.41
635111	Drill Core	0.60	<0.001	0.001	0.21	0.73	<2	0.003	<0.001	0.06	0.85	<0.02	0.01	0.002	<0.01	<0.01	23.65	0.03	<0.001	0.08	0.29
635112	Drill Core	2.31	0.001	0.002	0.10	0.82	<2	0.003	<0.001	0.02	0.58	<0.02	<0.01	0.002	<0.01	<0.01	12.26	0.03	0.001	0.05	0.33
635113	Drill Core	1.24	0.002	0.005	2.96	3.02	3	0.006	<0.001	0.02	2.00	<0.02	<0.01	0.008	<0.01	<0.01	6.79	0.04	0.002	0.06	0.62
635114	Drill Core	1.27	<0.001	0.001	0.60	2.55	2	0.002	<0.001	0.07	0.95	<0.02	0.02	0.008	<0.01	<0.01	29.22	0.06	<0.001	0.12	0.24
635115	Drill Core	1.69	0.001	0.004	1.11	4.67	3	0.006	<0.001	0.03	2.22	<0.02	<0.01	0.014	<0.01	<0.01	12.34	0.10	0.003	0.13	0.95
635116	Drill Core	1.60	<0.001	0.002	0.46	2.09	<2	0.004	<0.001	0.03	1.60	<0.02	0.01	0.006	<0.01	<0.01	18.27	0.07	0.002	0.09	0.49
635117	Drill Core	1.16	0.002	0.004	0.90	3.26	<2	0.009	<0.001	0.02	2.42	<0.02	<0.01	0.009	<0.01	<0.01	6.26	0.13	0.002	0.14	1.41
635118	Drill Core	1.41	0.002	0.003	2.01	7.05	3	0.005	<0.001	0.04	2.63	<0.02	0.01	0.022	<0.01	<0.01	21.70	0.04	<0.001	0.09	0.50
635119	Drill Core	1.64	0.002	0.005	1.79	12.75	4	0.006	<0.001	0.04	3.49	<0.02	0.01	0.031	<0.01	<0.01	17.41	0.04	0.001	0.09	0.49
635120	Rock	0.42	<0.001	0.001	<0.02	0.07	<2	0.003	<0.001	0.02	0.42	<0.02	<0.01	<0.001	<0.01	<0.01	19.98	0.02	0.001	10.78	0.37
635121	Drill Core	2.17	0.001	0.002	2.47	4.87	2	0.005	<0.001	0.03	1.65	<0.02	<0.01	0.014	<0.01	<0.01	11.86	0.07	0.001	0.11	0.62
635122	Drill Core	1.70	0.002	0.002	0.77	3.30	<2	0.006	<0.001	0.03	1.63	<0.02	<0.01	0.010	<0.01	<0.01	10.96	0.04	0.002	0.10	0.73
635123	Drill Core	0.91	0.004	0.009	>10	21.16	14	0.012	<0.001	0.02	8.09	<0.02	<0.01	0.064	<0.01	<0.01	2.71	0.07	0.003	0.10	0.76
635124	Drill Core	0.99	0.001	0.006	>10	34.31	11	0.004	<0.001	0.01	2.05	<0.02	<0.01	0.113	0.01	<0.01	0.43	0.05	0.002	0.03	0.28
635125	Drill Core	0.70	0.001	0.004	8.40	26.75	6	0.004	<0.001	0.01	1.79	<0.02	<0.01	0.077	0.01	<0.01	0.94	0.05	0.002	0.04	0.31
635126	Drill Core	1.78	0.003	0.004	2.47	7.69	4	0.009	<0.001	0.02	2.46	<0.02	<0.01	0.025	<0.01	<0.01	7.76	0.10	0.003	0.13	1.18
635127	Drill Core	1.31	<0.001	0.003	7.83	25.08	4	0.001	<0.001	0.03	1.72	<0.02	<0.01	0.090	<0.01	<0.01	10.10	0.08	<0.001	0.03	0.07
635128	Drill Core	1.06	<0.001	0.004	8.23	29.72	6	0.002	<0.001	0.02	0.42	<0.02	<0.01	0.104	0.01	<0.01	15.46	0.12	<0.001	0.03	0.07
635129	Drill Core	0.43	0.002	<0.001	1.04	4.51	<2	0.008	<0.001	0.01	0.51	<0.02	<0.01	0.014	<0.01	<0.01	5.31	0.16	0.002	0.11	0.97
635130	Rock Pulp	0.06	<0.001	0.491	1.48	2.96	18	<0.001	<0.001	0.45	2.52	<0.02	0.02	0.018	<0.01	<0.01	4.89	0.02	<0.001	0.32	4.30



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: January 13, 2011

Page: 2 of 3 **Part** 2

CERTIFICATE OF ANALYSIS

WHI10000692.1

	Method Analyte Unit MDL	7TD	7TD	7TD	7TD	G8SG	7TD.1
		Na	K	W	S	SG	Pb
		%	%	%	%		%
		0.01	0.01	0.01	0.05	0	0.02
635101	Drill Core	<0.01	0.79	<0.01	0.86	2.42	
635102	Drill Core	0.01	0.12	<0.01	0.48	2.56	
635103	Drill Core	<0.01	0.85	<0.01	1.21	2.34	
635104	Drill Core	<0.01	0.50	<0.01	9.13	2.71	
635105	Drill Core	<0.01	0.92	<0.01	9.42	2.56	
635106	Drill Core	<0.01	0.68	<0.01	17.96	2.85	
635107	Drill Core	<0.01	0.30	<0.01	13.86	2.93	
635108	Drill Core	<0.01	0.71	<0.01	11.53	2.55	
635109	Drill Core	<0.01	0.41	<0.01	7.22	2.60	
635110	Drill Core	<0.01	0.21	<0.01	1.60	2.53	
635111	Drill Core	<0.01	0.15	<0.01	1.27	2.48	
635112	Drill Core	<0.01	0.17	<0.01	0.90	2.45	
635113	Drill Core	<0.01	0.34	<0.01	3.66	2.51	
635114	Drill Core	<0.01	0.12	<0.01	2.28	2.60	
635115	Drill Core	<0.01	0.52	<0.01	4.61	2.58	
635116	Drill Core	<0.01	0.24	<0.01	2.68	2.49	
635117	Drill Core	<0.01	0.80	<0.01	4.14	2.41	
635118	Drill Core	<0.01	0.24	<0.01	6.70	2.62	
635119	Drill Core	<0.01	0.24	<0.01	10.27	2.66	
635120	Rock	0.01	0.03	<0.01	0.10	2.68	
635121	Drill Core	<0.01	0.35	<0.01	4.31	2.51	
635122	Drill Core	<0.01	0.41	<0.01	3.26	2.50	
635123	Drill Core	<0.01	0.40	<0.01	20.25	3.18	11.32
635124	Drill Core	<0.01	0.15	<0.01	19.13	3.33	13.73
635125	Drill Core	<0.01	0.17	<0.01	14.85	3.12	
635126	Drill Core	<0.01	0.67	<0.01	6.82	2.52	
635127	Drill Core	<0.01	0.04	<0.01	14.22	3.12	
635128	Drill Core	<0.01	0.04	<0.01	15.12	3.14	
635129	Drill Core	<0.01	0.57	<0.01	2.64	2.41	
635130	Rock Pulp	1.71	1.26	<0.01	2.99	N.A.	



Acme Analytical Laboratories (Vancouver) Ltd.
1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: January 13, 2011

Page: 3 of 3 Part 1

CERTIFICATE OF ANALYSIS

WHI10000692.1

	Method Analyte Unit MDL	WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD
		Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg	Al
		kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%	%
		0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01	0.01
635131	Drill Core	1.62	<0.001	0.002	8.15	32.70	4	<0.001	<0.001	0.01	1.50	<0.02	<0.01	0.115	0.01	<0.01	4.31	0.05	<0.001	0.02	0.07
635132	Drill Core	1.75	<0.001	0.001	6.64	24.18	3	<0.001	<0.001	0.04	0.41	<0.02	<0.01	0.089	<0.01	<0.01	17.55	0.07	<0.001	0.06	0.05
635133	Drill Core	2.59	<0.001	0.002	6.67	23.74	<2	0.002	<0.001	0.03	1.23	<0.02	<0.01	0.090	<0.01	<0.01	13.03	0.28	<0.001	0.04	0.05
635134	Drill Core	2.07	0.002	0.003	0.10	0.17	<2	0.007	<0.001	0.03	0.97	<0.02	0.01	<0.001	<0.01	<0.01	14.61	0.07	0.002	0.14	0.92
635135	Drill Core	1.72	0.003	0.006	0.68	0.40	<2	0.009	<0.001	0.02	2.35	<0.02	<0.01	0.001	<0.01	<0.01	10.33	0.07	0.003	0.15	1.29
635136	Drill Core	1.85	0.002	0.003	0.09	0.56	<2	0.005	<0.001	0.03	0.81	<0.02	<0.01	0.002	<0.01	<0.01	7.06	0.04	0.002	0.09	0.54
635137	Drill Core	1.04	0.003	0.007	0.12	0.27	<2	0.008	<0.001	0.03	1.12	<0.02	0.02	<0.001	<0.01	<0.01	15.28	0.23	0.004	0.18	1.10
635138	Drill Core	1.29	0.002	0.007	<0.02	<0.01	<2	0.012	<0.001	0.02	2.54	<0.02	<0.01	<0.001	<0.01	<0.01	7.02	0.07	0.010	0.66	4.79
635139	Drill Core	1.22	<0.001	0.004	<0.02	<0.01	<2	0.006	<0.001	0.02	1.55	<0.02	<0.01	<0.001	<0.01	<0.01	5.73	0.07	0.008	0.52	5.13
635140	Drill Core	0.62	<0.001	0.004	<0.02	<0.01	<2	0.007	<0.001	0.02	1.43	<0.02	<0.01	<0.001	<0.01	<0.01	6.16	0.11	0.009	0.58	5.03
635141	Drill Core	0.67	<0.001	0.004	<0.02	<0.01	<2	0.008	<0.001	0.02	1.82	<0.02	<0.01	<0.001	<0.01	<0.01	7.78	0.40	0.010	0.62	5.69



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: January 13, 2011

Page: 3 of 3 **Part** 2

CERTIFICATE OF ANALYSIS

WHI10000692.1

	Method	7TD	7TD	7TD	7TD	G8SG	7TD.1
	Analyte	Na	K	W	S	SG	Pb
	Unit	%	%	%	%		%
	MDL	0.01	0.01	0.01	0.05	0	0.02
635131	Drill Core	<0.01	0.04	<0.01	17.20	3.26	
635132	Drill Core	<0.01	0.02	<0.01	12.38	3.09	
635133	Drill Core	<0.01	0.04	<0.01	13.38	3.18	
635134	Drill Core	<0.01	0.60	<0.01	1.09	2.44	
635135	Drill Core	<0.01	0.83	<0.01	3.04	2.40	
635136	Drill Core	<0.01	0.31	<0.01	1.04	2.40	
635137	Drill Core	<0.01	0.81	<0.01	1.10	2.45	
635138	Drill Core	<0.01	2.77	<0.01	2.73	2.37	
635139	Drill Core	0.01	3.70	<0.01	1.45	2.42	
635140	Drill Core	0.01	4.19	<0.01	1.22	2.40	
635141	Drill Core	0.01	3.84	<0.01	1.77	2.42	



Acme Analytical Laboratories (Vancouver) Ltd.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: **Selwyn Resources Ltd.**

Suite 700 - 509 Richards Street

Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: January 13, 2011

Page: 1 of 2 Part 1

QUALITY CONTROL REPORT

WHI10000692.1

	Method Analyte Unit MDL	WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD
		Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg	Al
		kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%	%
		0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.01	0.001	0.01
Pulp Duplicates																					
635120	Rock	0.42	<0.001	0.001	<0.02	0.07	<2	0.003	<0.001	0.02	0.42	<0.02	<0.01	<0.001	<0.01	<0.01	19.98	0.02	0.001	10.78	0.37
REP 635120	QC		<0.001	0.002	<0.02	0.07	<2	0.003	<0.001	0.02	0.44	<0.02	<0.01	<0.001	<0.01	<0.01	20.23	0.02	<0.001	10.94	0.37
635123	Drill Core	0.91	0.004	0.009	>10	21.16	14	0.012	<0.001	0.02	8.09	<0.02	<0.01	0.064	<0.01	<0.01	2.71	0.07	0.003	0.10	0.76
REP 635123	QC																				
635141	Drill Core	0.67	<0.001	0.004	<0.02	<0.01	<2	0.008	<0.001	0.02	1.82	<0.02	<0.01	<0.001	<0.01	<0.01	7.78	0.40	0.010	0.62	5.69
REP 635141	QC		<0.001	0.004	<0.02	<0.01	<2	0.008	<0.001	0.02	1.82	<0.02	<0.01	<0.001	<0.01	<0.01	7.86	0.40	0.009	0.63	5.73
Core Reject Duplicates																					
635127	Drill Core	1.31	<0.001	0.003	7.83	25.08	4	0.001	<0.001	0.03	1.72	<0.02	<0.01	0.090	<0.01	<0.01	10.10	0.08	<0.001	0.03	0.07
DUP 635127	QC		<0.001	0.002	8.81	23.62	5	0.002	<0.001	0.03	2.13	<0.02	<0.01	0.087	<0.01	<0.01	11.36	0.09	<0.001	0.03	0.08
Reference Materials																					
STD CCU-1C	Standard																				
STD CZN-3	Standard																				
STD OREAS131A	Standard		<0.001	0.032	1.77	2.92	32	0.003	0.002	0.17	5.87	<0.02	<0.01	0.008	<0.01	<0.01	5.42	0.06	0.002	3.17	4.68
STD OREAS131A	Standard		<0.001	0.032	1.76	2.90	32	0.003	0.002	0.18	5.71	<0.02	<0.01	0.008	<0.01	<0.01	5.18	0.06	0.002	3.19	4.70
STD PTC-1A	Standard																				
STD R4T	Standard		0.064	0.502	1.55	3.45	87	0.352	0.040	0.09	23.98	<0.02	0.02	0.019	0.02	<0.01	2.18	0.04	0.018	1.41	3.94
STD R4T	Standard		0.065	0.512	1.55	3.47	89	0.354	0.040	0.09	24.27	<0.02	0.02	0.018	0.02	<0.01	2.19	0.05	0.018	1.43	3.95
STD SARM 71	Standard																				
STD SU-1B	Standard		<0.001	1.190	<0.02	0.03	7	1.984	0.067	0.07	25.32	<0.02	0.03	<0.001	<0.01	<0.01	2.24	0.06	0.031	1.80	4.43
STD SU-1B	Standard		<0.001	1.170	<0.02	0.03	7	1.915	0.064	0.07	25.52	<0.02	0.03	<0.001	<0.01	<0.01	2.24	0.06	0.028	1.82	4.42
STD R4T Expected			0.062	0.502	1.518	3.376	86	0.339	0.039	0.086	24.07	0.0087	0.0185	0.018	0.0138	0.0018	2.166	0.045	0.018	1.384	3.897
STD OREAS131A Expected			0.001	0.0322	1.72	2.83	30.9	0.0027	0.0023	0.1722	5.8166	0.0082	0.0028	0.0081	0.0047	0.001	5.286	0.0536	0.0025	3.1182	4.6057
STD SU-1B Expected			0.0004	1.185	0.0058	0.0235	6.4	1.97	0.0672	0.0703	25.54	0.00025	0.03	0.0003	0.00002	0.0003	2.21	0.06	0.032	1.79	4.39
STD CZN-3 Expected																					
STD CCU-1C Expected																					
STD PTC-1A Expected																					
BLK	Blank		<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	<0.01	<0.01	<0.02	<0.01	<0.001	<0.01	<0.01	<0.01	<0.01	<0.001	<0.01	<0.01
BLK	Blank		<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	<0.01	<0.01	<0.02	<0.01	<0.001	<0.01	<0.01	<0.01	<0.01	<0.001	<0.01	<0.01



Acme Analytical Laboratories (Vancouver) Ltd.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: Selwyn Resources Ltd.

Suite 700 - 509 Richards Street

Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: January 13, 2011

Page: 1 of 2 **Part** 2

QUALITY CONTROL REPORT

WHI10000692.1

Method		7TD	7TD	7TD	7TD	G8SG	7TD.1
Analyte		Na	K	W	S	SG	Pb
Unit		%	%	%	%		%
MDL		0.01	0.01	0.01	0.05	0	0.02
Pulp Duplicates							
635120	Rock	0.01	0.03	<0.01	0.10	2.68	
REP 635120	QC	0.01	0.03	<0.01	0.10		
635123	Drill Core	<0.01	0.40	<0.01	20.25	3.18	11.32
REP 635123	QC						11.39
635141	Drill Core	0.01	3.84	<0.01	1.77	2.42	
REP 635141	QC	0.01	3.91	<0.01	1.76		
Core Reject Duplicates							
635127	Drill Core	<0.01	0.04	<0.01	14.22	3.12	
DUP 635127	QC	<0.01	0.04	<0.01	14.14	3.12	
Reference Materials							
STD CCU-1C	Standard						0.39
STD CZN-3	Standard						0.11
STD OREAS131A	Standard	0.16	3.43	<0.01	5.01		
STD OREAS131A	Standard	0.15	3.46	<0.01	4.46		
STD PTC-1A	Standard						0.06
STD R4T	Standard	0.91	1.17	<0.01	12.82		
STD R4T	Standard	0.91	1.15	<0.01	11.55		
STD SARM 71	Standard						<0.02
STD SU-1B	Standard	1.70	0.62	<0.01	9.13		
STD SU-1B	Standard	1.69	0.61	<0.01	7.90		
STD R4T Expected		0.9	1.153	0.00016	12.9903		
STD OREAS131A Expected		0.1501	3.1584	0.0005	4.8		
STD SU-1B Expected		1.662	0.6	0.0007	8.76		
STD CZN-3 Expected							0.113
STD CCU-1C Expected							0.34
STD PTC-1A Expected							0.05
BLK	Blank	<0.01	<0.01	<0.01	<0.05		
BLK	Blank	<0.01	<0.01	<0.01	<0.05		



Acme Analytical Laboratories (Vancouver) Ltd.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: **Selwyn Resources Ltd.**

Suite 700 - 509 Richards Street

Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: January 13, 2011

Page: 2 of 2 Part 1

QUALITY CONTROL REPORT

WHI10000692.1

		WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD
		Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg
		kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%
		0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01
BLK	Blank																			
Prep Wash																				
G1	Prep Blank	<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	0.07	2.08	<0.02	0.07	<0.001	<0.01	<0.01	2.13	0.07	0.001	0.57	6.17
G1	Prep Blank	<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	0.07	2.12	<0.02	0.07	<0.001	<0.01	<0.01	2.37	0.07	<0.001	0.61	6.60



Acme Analytical Laboratories (Vancouver) Ltd.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: **Selwyn Resources Ltd.**

Suite 700 - 509 Richards Street

Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: January 13, 2011

Page: 2 of 2 **Part** 2

QUALITY CONTROL REPORT

WHI10000692.1

		7TD	7TD	7TD	7TD	G8SG	7TD.1
		Na	K	W	S	SG	Pb
		%	%	%	%		%
		0.01	0.01	0.01	0.05	0	0.02
BLK	Blank						
Prep Wash							
G1	Prep Blank	2.63	3.02	<0.01	<0.05	2.67	
G1	Prep Blank	2.70	3.04	<0.01	<0.05	2.67	



1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: Selwyn Resources Ltd.

Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Submitted By: Jason K. Dunning

Receiving Lab: Canada-Whitehorse

Received: December 13, 2010

Report Date: December 30, 2010

Page: 1 of 6

CERTIFICATE OF ANALYSIS

WHI10000690.1

CLIENT JOB INFORMATION

Project: Selwyn Project
Shipment ID:
P.O. Number 1156
Number of Samples: 133

SAMPLE DISPOSAL

STOR-PLP Store After 90 days Invoice for Storage
STOR-RJT Store After 90 days Invoice for Storage

Acme does not accept responsibility for samples left at the laboratory after 90 days without prior written instructions for sample storage or return.

Invoice To: Selwyn Resources Ltd.
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6
Canada

CC:

SAMPLE PREPARATION AND ANALYTICAL PROCEDURES

Method Code	Number of Samples	Code Description	Test Wgt (g)	Report Status	Lab
7TD.1	11	4 Acid digestion ICP-ES analysis	0.1	Completed	VAN
R200-250	129	Crush split and pulverize 250g drill core to 200 mesh			WHI
7TD2	133	4 Acid digestion ICP-ES analysis.	0.5	Completed	VAN
G812	133	Specific Gravity on Pulp		Completed	VAN

ADDITIONAL COMMENTS



This report supersedes all previous preliminary and final reports with this file number dated prior to the date on this certificate. Signature indicates final approval; preliminary reports are unsigned and should be used for reference only.
All results are considered the confidential property of the client. Acme assumes the liabilities for actual cost of analysis only.
** asterisk indicates that an analytical result could not be provided due to unusually high levels of interference from other elements.



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: December 30, 2010

Page: 2 of 6 Part 1

CERTIFICATE OF ANALYSIS

WHI10000690.1

	Method Analyte Unit MDL	7TD.1	WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD
		Pb	Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg
		%	kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%
		0.02	0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01
631551	Drill Core		1.87	<0.001	0.004	0.04	0.17	<2	0.008	<0.001	0.01	1.26	<0.02	<0.01	<0.001	<0.01	<0.01	8.18	0.61	0.005	0.16
631552	Drill Core		2.24	0.001	0.006	<0.02	0.16	<2	0.008	<0.001	<0.01	1.09	<0.02	<0.01	<0.001	<0.01	<0.01	4.47	1.08	0.005	0.14
631553	Drill Core		1.29	<0.001	0.004	0.52	0.08	<2	0.008	<0.001	<0.01	0.93	<0.02	<0.01	<0.001	<0.01	<0.01	3.26	0.80	0.004	0.12
631554	Drill Core		1.16	<0.001	0.002	<0.02	0.26	<2	0.005	<0.001	<0.01	0.64	<0.02	<0.01	<0.001	<0.01	<0.01	5.98	0.97	0.003	0.10
631555	Drill Core		2.26	0.001	0.004	<0.02	0.19	<2	0.008	<0.001	0.01	1.00	<0.02	<0.01	<0.001	<0.01	<0.01	5.21	0.90	0.004	0.12
631556	Drill Core		1.09	<0.001	0.015	1.20	0.02	<2	0.003	<0.001	0.04	5.64	<0.02	0.01	<0.001	<0.01	<0.01	23.18	0.18	0.001	0.08
631557	Drill Core		1.81	0.002	0.008	<0.02	0.13	<2	0.009	<0.001	0.01	0.97	<0.02	<0.01	<0.001	<0.01	<0.01	5.09	0.66	0.004	0.13
631558	Drill Core		1.61	0.002	0.005	<0.02	0.32	<2	0.010	<0.001	<0.01	0.89	<0.02	<0.01	0.001	<0.01	<0.01	2.51	0.89	0.004	0.13
631559	Drill Core		0.75	0.003	0.009	0.04	0.63	3	0.013	<0.001	<0.01	0.97	<0.02	<0.01	0.003	<0.01	<0.01	1.67	0.54	0.005	0.19
631560	Rock Pulp		0.06	<0.001	0.476	1.47	2.98	19	<0.001	<0.001	0.43	2.65	<0.02	0.02	0.018	<0.01	<0.01	5.05	0.01	0.001	0.33
631561	Drill Core		1.28	0.003	0.013	0.03	0.35	<2	0.012	<0.001	<0.01	3.52	<0.02	<0.01	0.002	<0.01	<0.01	2.79	0.67	0.004	0.18
631562	Drill Core		1.75	0.004	0.008	0.22	0.42	<2	0.012	<0.001	<0.01	2.18	<0.02	<0.01	0.002	<0.01	<0.01	0.80	0.26	0.004	0.15
631563	Drill Core		2.66	0.003	0.004	0.12	0.89	2	0.012	<0.001	<0.01	1.14	<0.02	<0.01	0.005	<0.01	<0.01	1.04	0.23	0.004	0.14
631564	Drill Core		1.07	0.007	0.011	3.56	7.10	6	0.012	<0.001	0.03	4.86	<0.02	<0.01	0.035	<0.01	<0.01	6.18	0.09	0.004	0.18
631565	Drill Core		1.04	<0.001	0.007	0.76	3.03	2	0.005	<0.001	0.03	10.47	<0.02	0.01	0.015	<0.01	<0.01	20.48	0.05	0.002	0.11
631566	Drill Core		2.60	<0.001	0.003	0.99	3.23	<2	0.004	<0.001	0.05	1.14	<0.02	0.02	0.018	<0.01	<0.01	27.70	0.06	0.002	0.20
631567	Drill Core		2.89	<0.001	0.002	0.69	2.18	<2	0.003	<0.001	0.05	0.77	<0.02	0.02	0.012	<0.01	<0.01	29.75	0.04	0.001	0.15
631568	Drill Core		3.25	<0.001	0.003	1.17	2.21	<2	0.003	<0.001	0.05	2.19	<0.02	0.01	0.008	<0.01	<0.01	29.16	0.02	0.001	0.08
631569	Drill Core		3.22	0.005	0.010	3.08	7.28	4	0.013	<0.001	0.03	7.16	<0.02	<0.01	0.026	<0.01	<0.01	5.64	0.06	0.003	0.14
631570	Drill Core		0.94	0.006	0.013	1.16	9.41	5	0.013	<0.001	0.02	9.87	<0.02	<0.01	0.032	<0.01	<0.01	0.30	0.07	0.004	0.13
631571	Drill Core		1.22	0.006	0.012	2.32	9.82	4	0.012	<0.001	0.02	9.24	<0.02	<0.01	0.034	<0.01	<0.01	0.33	0.06	0.004	0.12
631572	Drill Core		2.21	0.003	0.009	0.94	5.72	3	0.010	<0.001	0.01	8.08	<0.02	<0.01	0.016	<0.01	<0.01	0.58	0.04	0.003	0.08
631573	Drill Core		2.15	0.003	0.006	1.38	6.34	<2	0.008	<0.001	0.03	3.29	<0.02	<0.01	0.016	<0.01	<0.01	8.70	0.07	0.002	0.10
631574	Drill Core		1.77	0.001	0.002	0.94	2.11	<2	0.003	<0.001	0.03	1.00	<0.02	<0.01	0.006	<0.01	<0.01	16.13	0.04	0.001	0.06
631575	Drill Core		1.27	<0.001	0.002	0.05	0.49	<2	0.003	<0.001	0.03	0.95	<0.02	0.01	0.001	<0.01	<0.01	19.86	0.03	<0.001	0.05
631576	Drill Core		1.32	0.001	0.001	0.03	0.63	<2	0.003	<0.001	<0.01	0.54	<0.02	<0.01	0.002	<0.01	<0.01	3.34	0.03	0.002	0.04
631577	Drill Core		2.20	0.005	0.007	0.07	0.50	<2	0.013	<0.001	<0.01	3.52	<0.02	<0.01	0.002	<0.01	<0.01	1.80	0.06	0.004	0.12
631578	Drill Core		2.19	0.008	0.003	0.03	0.30	<2	0.013	<0.001	<0.01	1.52	<0.02	<0.01	<0.001	<0.01	<0.01	0.51	0.04	0.004	0.12
631579	Drill Core		1.73	0.004	0.014	3.90	12.48	<2	0.009	<0.001	0.03	7.67	<0.02	<0.01	0.033	<0.01	<0.01	2.38	0.06	0.003	0.07
631580	Rock		0.34	<0.001	<0.001	<0.02	0.01	<2	<0.001	<0.001	0.02	0.18	<0.02	<0.01	<0.001	<0.01	<0.01	21.67	0.03	<0.001	11.35



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: Selwyn Resources Ltd.
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: December 30, 2010

Page: 2 of 6 **Part** 2

CERTIFICATE OF ANALYSIS

WHI10000690.1

	Method Analyte Unit MDL	7TD	7TD	7TD	7TD	7TD	G8SG
		Al	Na	K	W	S	SG
		%	%	%	%	%	
		0.01	0.01	0.01	0.01	0.05	0
631551	Drill Core	1.58	<0.01	1.02	<0.01	1.44	2.31
631552	Drill Core	1.53	<0.01	0.91	<0.01	1.17	2.30
631553	Drill Core	1.37	<0.01	1.05	<0.01	1.08	2.38
631554	Drill Core	1.01	<0.01	0.63	<0.01	0.73	2.39
631555	Drill Core	1.29	<0.01	0.83	<0.01	1.14	2.32
631556	Drill Core	0.22	<0.01	0.13	<0.01	6.94	2.62
631557	Drill Core	1.31	<0.01	0.80	<0.01	1.06	2.25
631558	Drill Core	1.34	<0.01	0.79	<0.01	1.08	2.20
631559	Drill Core	2.00	<0.01	1.14	<0.01	1.31	2.22
631560	Rock Pulp	4.26	1.74	1.28	<0.01	3.32	N.A.
631561	Drill Core	1.95	<0.01	1.14	<0.01	4.26	2.20
631562	Drill Core	1.68	<0.01	0.99	<0.01	2.69	2.17
631563	Drill Core	1.64	<0.01	0.98	<0.01	1.67	2.16
631564	Drill Core	2.04	<0.01	1.20	<0.01	9.83	2.46
631565	Drill Core	0.78	<0.01	0.50	<0.01	14.38	2.83
631566	Drill Core	1.01	<0.01	0.53	<0.01	3.15	2.55
631567	Drill Core	0.60	<0.01	0.30	<0.01	2.12	2.57
631568	Drill Core	0.33	<0.01	0.21	<0.01	3.95	2.57
631569	Drill Core	1.64	<0.01	0.97	<0.01	12.60	2.42
631570	Drill Core	1.82	<0.01	1.10	<0.01	16.45	2.33
631571	Drill Core	1.65	<0.01	1.01	<0.01	16.03	2.45
631572	Drill Core	0.89	<0.01	0.54	<0.01	12.50	2.46
631573	Drill Core	0.90	<0.01	0.54	<0.01	7.41	2.38
631574	Drill Core	0.38	<0.01	0.21	<0.01	2.34	2.45
631575	Drill Core	0.23	<0.01	0.12	<0.01	1.37	2.41
631576	Drill Core	0.34	<0.01	0.16	<0.01	0.76	2.34
631577	Drill Core	1.42	<0.01	0.87	<0.01	4.33	2.13
631578	Drill Core	1.73	<0.01	1.19	<0.01	1.77	2.02
631579	Drill Core	0.75	<0.01	0.40	<0.01	15.78	2.66
631580	Rock	0.07	<0.01	0.21	<0.01	<0.05	2.56



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**

Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: December 30, 2010

Page: 3 of 6 Part 1

CERTIFICATE OF ANALYSIS

WHI10000690.1

	Method Analyte Unit MDL	7TD.1	WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD
		Pb	Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg
		%	kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%
		0.02	0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01
631581	Drill Core		2.63	0.004	0.012	2.19	12.01	3	0.009	<0.001	0.04	8.28	<0.02	<0.01	0.033	<0.01	<0.01	4.22	0.06	0.002	0.08
631582	Drill Core		2.79	<0.001	<0.001	0.05	0.47	<2	<0.001	<0.001	0.07	0.67	<0.02	0.01	0.001	<0.01	<0.01	31.74	0.03	<0.001	0.11
631583	Drill Core		2.22	0.002	0.004	1.20	5.67	<2	0.007	<0.001	0.02	2.99	<0.02	<0.01	0.015	<0.01	<0.01	4.76	0.09	0.003	0.12
631584	Drill Core		1.86	0.001	0.003	0.66	3.89	<2	0.006	<0.001	0.04	2.29	<0.02	<0.01	0.010	<0.01	<0.01	17.32	0.09	0.003	0.14
631585	Drill Core		2.69	0.001	0.003	1.08	4.18	<2	0.003	<0.001	0.04	2.56	<0.02	0.01	0.012	<0.01	<0.01	24.17	0.06	0.001	0.09
631586	Drill Core		1.90	0.001	0.003	0.84	3.92	<2	0.005	<0.001	0.02	2.52	<0.02	<0.01	0.010	<0.01	<0.01	8.18	0.07	0.002	0.08
631587	Drill Core		1.71	0.002	0.004	1.47	7.90	2	0.007	<0.001	0.03	3.29	<0.02	<0.01	0.023	<0.01	<0.01	7.99	0.09	0.002	0.10
631588	Drill Core		1.53	<0.001	0.003	2.38	9.01	2	0.005	<0.001	0.03	1.66	<0.02	<0.01	0.030	<0.01	<0.01	17.38	0.07	0.002	0.10
631589	Drill Core		3.56	<0.001	0.003	7.99	22.67	5	0.002	<0.001	0.02	1.62	<0.02	<0.01	0.083	<0.01	<0.01	6.83	0.05	0.001	0.04
631590	Rock Pulp		0.06	<0.001	0.668	5.97	6.78	71	<0.001	<0.001	0.09	5.04	<0.02	0.02	0.018	0.04	<0.01	1.40	0.03	<0.001	0.26
631591	Drill Core		0.93	0.001	0.003	1.08	3.85	<2	0.006	<0.001	0.04	1.40	<0.02	0.01	0.011	<0.01	<0.01	23.41	0.10	0.002	0.15
631592	Drill Core		0.62	0.002	0.001	0.47	0.42	<2	0.006	<0.001	0.01	0.64	<0.02	<0.01	0.002	<0.01	<0.01	10.27	0.10	0.002	0.14
631593	Drill Core		1.17	<0.001	0.002	9.56	7.63	3	0.001	<0.001	0.04	0.63	<0.02	0.01	0.042	<0.01	<0.01	21.97	0.04	<0.001	0.07
631594	Drill Core		0.42	0.002	0.004	8.37	1.52	3	0.007	<0.001	0.03	2.15	<0.02	<0.01	0.008	<0.01	<0.01	14.01	0.12	0.003	0.17
631595	Drill Core	11.90	1.42	<0.001	0.003	>10	18.45	4	0.002	<0.001	0.03	1.90	<0.02	<0.01	0.086	<0.01	<0.01	11.09	0.03	<0.001	0.05
631596	Drill Core		1.41	<0.001	0.002	9.98	16.62	3	<0.001	<0.001	0.04	0.86	<0.02	<0.01	0.077	<0.01	<0.01	19.12	0.02	<0.001	0.04
631597	Drill Core		1.43	<0.001	<0.001	7.06	10.33	<2	<0.001	<0.001	0.05	1.38	<0.02	<0.01	0.045	<0.01	<0.01	24.08	0.03	<0.001	0.05
631598	Drill Core		1.25	<0.001	<0.001	6.67	12.06	<2	<0.001	<0.001	0.05	0.48	<0.02	<0.01	0.055	<0.01	<0.01	26.39	0.02	<0.001	0.05
631599	Drill Core		1.43	<0.001	<0.001	7.77	13.12	<2	<0.001	<0.001	0.04	0.55	<0.02	<0.01	0.062	<0.01	<0.01	21.74	0.02	<0.001	0.04
631600	Drill Core	12.64	0.65	<0.001	0.002	>10	20.85	<2	<0.001	<0.001	0.02	0.21	<0.02	<0.01	0.103	<0.01	<0.01	13.85	0.03	<0.001	0.02
631601	Drill Core		1.01	<0.001	0.008	0.08	0.11	<2	0.014	<0.001	<0.01	1.70	<0.02	<0.01	<0.001	<0.01	<0.01	5.39	1.96	0.011	0.78
631602	Drill Core		1.58	<0.001	0.004	0.03	0.08	<2	0.009	<0.001	0.02	1.16	<0.02	0.02	<0.001	<0.01	<0.01	14.76	1.65	0.007	0.58
631603	Drill Core		0.67	<0.001	0.009	0.43	7.16	6	0.005	<0.001	0.02	3.58	<0.02	0.01	0.018	<0.01	<0.01	11.70	0.16	0.003	0.21
631604	Drill Core		0.85	<0.001	0.004	0.08	0.09	<2	0.012	<0.001	<0.01	1.42	<0.02	<0.01	<0.001	<0.01	<0.01	6.09	1.83	0.009	0.61
631605	Drill Core		0.59	<0.001	0.005	0.03	0.02	<2	0.012	<0.001	0.02	1.70	<0.02	0.02	<0.001	<0.01	<0.01	11.26	1.65	0.009	0.62
631606	Drill Core		0.51	<0.001	0.004	0.19	0.69	<2	0.009	<0.001	0.02	0.81	<0.02	0.01	0.002	<0.01	<0.01	11.76	0.67	0.002	0.13
631607	Drill Core		0.90	<0.001	0.009	<0.02	0.10	<2	0.013	<0.001	0.01	1.53	<0.02	<0.01	<0.001	<0.01	<0.01	8.13	1.68	0.004	0.33
631608	Drill Core		1.04	<0.001	0.009	<0.02	0.24	<2	0.015	<0.001	<0.01	0.94	<0.02	<0.01	<0.001	<0.01	<0.01	5.55	1.88	0.007	0.28
631609	Drill Core		0.87	<0.001	0.005	<0.02	0.02	<2	0.013	<0.001	<0.01	0.79	<0.02	<0.01	<0.001	<0.01	<0.01	2.83	0.45	0.004	0.18
631610	Drill Core		0.41	<0.001	0.005	<0.02	0.26	<2	0.014	<0.001	0.01	1.05	<0.02	<0.01	<0.001	<0.01	<0.01	6.95	0.76	0.005	0.16



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: Selwyn Resources Ltd.

Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: December 30, 2010

Page: 3 of 6 **Part** 2

CERTIFICATE OF ANALYSIS

WHI10000690.1

	Method Analyte Unit MDL	7TD	7TD	7TD	7TD	7TD	G8SG
		Al	Na	K	W	S	SG
		%	%	%	%	%	
		0.01	0.01	0.01	0.01	0.05	0
631581	Drill Core	0.71	<0.01	0.40	<0.01	16.13	2.61
631582	Drill Core	0.08	<0.01	0.06	<0.01	1.07	2.51
631583	Drill Core	1.04	<0.01	0.61	<0.01	7.09	2.42
631584	Drill Core	0.96	<0.01	0.57	<0.01	4.85	2.44
631585	Drill Core	0.45	<0.01	0.25	<0.01	5.30	2.53
631586	Drill Core	0.61	<0.01	0.36	<0.01	5.01	2.45
631587	Drill Core	0.79	<0.01	0.46	<0.01	8.15	2.53
631588	Drill Core	0.58	<0.01	0.33	<0.01	6.83	2.61
631589	Drill Core	0.23	<0.01	0.12	<0.01	14.22	3.04
631590	Rock Pulp	5.32	2.29	1.37	<0.01	5.74	N.A.
631591	Drill Core	0.77	<0.01	0.49	<0.01	3.75	2.46
631592	Drill Core	1.01	<0.01	0.59	<0.01	0.98	2.27
631593	Drill Core	0.09	<0.01	0.06	<0.01	5.96	2.90
631594	Drill Core	1.25	<0.01	0.70	<0.01	4.63	2.53
631595	Drill Core	0.20	<0.01	0.11	<0.01	13.00	3.11
631596	Drill Core	0.05	<0.01	0.03	<0.01	10.69	3.00
631597	Drill Core	<0.01	<0.01	0.02	<0.01	7.59	2.89
631598	Drill Core	<0.01	<0.01	0.01	<0.01	7.23	2.90
631599	Drill Core	<0.01	<0.01	0.01	<0.01	8.17	2.90
631600	Drill Core	0.02	<0.01	0.01	<0.01	12.42	3.16
631601	Drill Core	3.62	<0.01	2.35	<0.01	1.80	2.12
631602	Drill Core	2.66	<0.01	1.76	<0.01	1.21	2.16
631603	Drill Core	0.61	<0.01	0.43	<0.01	7.79	2.64
631604	Drill Core	3.29	<0.01	2.26	<0.01	1.49	2.07
631605	Drill Core	2.91	<0.01	1.90	<0.01	1.76	2.11
631606	Drill Core	1.41	<0.01	0.97	<0.01	1.21	2.39
631607	Drill Core	2.58	<0.01	1.44	<0.01	1.74	2.18
631608	Drill Core	2.31	<0.01	1.33	<0.01	1.14	2.07
631609	Drill Core	1.67	<0.01	1.05	<0.01	0.76	2.19
631610	Drill Core	1.60	<0.01	1.07	<0.01	1.22	2.20



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: December 30, 2010

Page: 4 of 6 Part 1

CERTIFICATE OF ANALYSIS

WHI10000690.1

	Method Analyte Unit MDL	7TD.1	WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD
		Pb	Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg
		%	kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%
		0.02	0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01
631611	Drill Core		0.38	<0.001	0.005	<0.02	0.42	<2	0.015	<0.001	0.01	1.20	<0.02	<0.01	<0.001	<0.01	<0.01	4.64	0.80	0.005	0.17
631612	Drill Core		1.57	<0.001	0.006	<0.02	0.04	<2	0.014	<0.001	<0.01	0.82	<0.02	<0.01	<0.001	<0.01	<0.01	6.99	2.23	0.007	0.17
631613	Drill Core		1.09	<0.001	0.003	<0.02	0.05	<2	0.013	<0.001	<0.01	0.81	<0.02	<0.01	<0.001	<0.01	<0.01	3.97	1.75	0.006	0.12
631614	Drill Core		1.53	<0.001	0.003	<0.02	0.12	<2	0.014	<0.001	<0.01	0.68	<0.02	<0.01	<0.001	<0.01	<0.01	6.95	2.71	0.010	0.14
631615	Drill Core		0.84	<0.001	0.010	<0.02	1.04	<2	0.009	<0.001	<0.01	2.02	<0.02	<0.01	0.002	<0.01	<0.01	7.12	2.34	0.006	0.10
631616	Drill Core		0.53	<0.001	0.003	<0.02	0.10	<2	0.009	<0.001	<0.01	0.56	<0.02	<0.01	<0.001	<0.01	<0.01	5.07	1.64	0.005	0.11
631617	Drill Core		2.37	<0.001	0.001	<0.02	0.03	<2	0.003	<0.001	0.06	0.32	<0.02	0.02	<0.001	<0.01	<0.01	30.94	0.40	<0.001	0.15
631618	Drill Core		2.46	<0.001	0.003	<0.02	0.18	<2	0.008	<0.001	<0.01	0.58	<0.02	<0.01	<0.001	<0.01	<0.01	3.12	1.29	0.006	0.09
631619	Drill Core		1.13	<0.001	0.002	<0.02	0.18	<2	0.007	<0.001	<0.01	0.57	<0.02	<0.01	<0.001	<0.01	<0.01	2.15	0.88	0.005	0.07
631620	Rock		0.36	<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	0.01	0.15	<0.02	0.01	<0.001	<0.01	<0.01	21.65	0.04	<0.001	11.30
631621	Drill Core		1.08	<0.001	0.007	<0.02	0.29	<2	0.011	<0.001	<0.01	1.19	<0.02	<0.01	<0.001	<0.01	<0.01	3.03	1.37	0.008	0.15
631622	Drill Core		0.89	<0.001	0.003	<0.02	0.17	<2	0.008	<0.001	<0.01	0.56	<0.02	<0.01	<0.001	<0.01	<0.01	1.10	0.46	0.004	0.11
631623	Drill Core		0.48	<0.001	0.006	<0.02	0.12	<2	0.005	<0.001	0.03	0.52	<0.02	0.01	<0.001	<0.01	<0.01	15.78	1.21	0.003	0.08
631624	Drill Core		0.94	<0.001	0.002	<0.02	0.18	<2	0.007	<0.001	<0.01	0.51	<0.02	<0.01	<0.001	<0.01	<0.01	3.03	0.73	0.004	0.07
631625	Drill Core		1.19	<0.001	0.006	0.25	0.50	3	0.009	<0.001	<0.01	0.81	<0.02	<0.01	0.001	<0.01	<0.01	5.62	1.27	0.005	0.10
631626	Drill Core		1.72	<0.001	0.007	<0.02	0.21	<2	0.010	<0.001	<0.01	0.97	<0.02	<0.01	<0.001	<0.01	<0.01	3.75	1.53	0.006	0.11
631627	Drill Core		2.54	<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	0.05	0.47	<0.02	0.02	<0.001	<0.01	<0.01	33.22	0.04	<0.001	0.12
631628	Drill Core		2.63	0.003	0.004	0.03	<0.01	<2	0.004	<0.001	0.02	2.10	<0.02	<0.01	<0.001	<0.01	<0.01	13.43	0.07	0.003	0.22
631629	Drill Core		0.60	0.008	0.009	0.20	1.41	2	0.007	<0.001	<0.01	1.10	<0.02	<0.01	0.004	<0.01	<0.01	3.32	0.09	0.003	0.23
631630	Rock Pulp		0.06	<0.001	0.656	5.87	6.68	69	<0.001	<0.001	0.09	4.94	<0.02	0.02	0.018	<0.01	<0.01	1.38	0.02	<0.001	0.26
631631	Drill Core		0.33	0.001	0.005	<0.02	3.00	<2	0.007	<0.001	<0.01	0.80	<0.02	<0.01	0.009	<0.01	<0.01	1.82	0.41	0.003	0.23
631632	Drill Core		0.76	0.008	0.004	0.02	2.02	<2	0.008	<0.001	<0.01	1.33	<0.02	<0.01	0.006	<0.01	<0.01	3.44	0.13	0.004	0.28
631633	Drill Core		2.13	<0.001	0.002	<0.02	<0.01	<2	<0.001	<0.001	0.05	1.49	<0.02	0.02	<0.001	<0.01	<0.01	28.57	0.02	<0.001	0.10
631634	Drill Core		1.20	0.004	0.008	0.79	<0.01	2	0.006	<0.001	0.02	2.73	<0.02	<0.01	<0.001	<0.01	<0.01	8.14	0.11	0.003	0.32
631635	Drill Core		0.48	0.010	0.030	0.44	1.68	4	0.014	<0.001	0.01	8.32	<0.02	<0.01	0.005	<0.01	<0.01	3.16	0.28	0.005	0.31
631636	Drill Core		1.81	0.002	0.005	0.03	0.40	<2	0.010	<0.001	<0.01	1.02	<0.02	<0.01	0.001	<0.01	<0.01	2.79	0.87	0.006	0.27
631637	Drill Core		0.40	0.001	0.004	<0.02	0.35	<2	0.006	<0.001	<0.01	0.69	<0.02	<0.01	0.001	<0.01	<0.01	0.92	0.19	0.004	0.16
631638	Drill Core		2.24	0.001	0.003	<0.02	0.13	<2	0.006	<0.001	<0.01	0.66	<0.02	<0.01	<0.001	<0.01	<0.01	2.10	0.47	0.004	0.15
631639	Drill Core		0.60	0.002	0.005	<0.02	0.77	2	0.009	<0.001	0.01	1.12	<0.02	<0.01	0.003	<0.01	<0.01	5.51	0.49	0.005	0.23
631640	Drill Core		0.44	0.003	0.004	<0.02	0.65	4	0.011	<0.001	<0.01	1.15	<0.02	<0.01	0.002	<0.01	<0.01	1.05	0.34	0.004	0.28



Acme Analytical Laboratories (Vancouver) Ltd.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: Selwyn Resources Ltd.

Suite 700 - 509 Richards Street

Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: December 30, 2010

Page: 4 of 6 Part 2

CERTIFICATE OF ANALYSIS

WHI10000690.1

	Method Analyte Unit MDL	7TD	7TD	7TD	7TD	7TD	G8SG
		Al	Na	K	W	S	SG
		%	%	%	%	%	
		0.01	0.01	0.01	0.01	0.05	0
631611	Drill Core	1.75	<0.01	1.16	<0.01	1.43	2.19
631612	Drill Core	1.61	<0.01	1.00	<0.01	0.84	2.21
631613	Drill Core	1.24	<0.01	0.80	<0.01	0.74	2.21
631614	Drill Core	1.51	<0.01	0.96	<0.01	0.69	2.16
631615	Drill Core	1.00	<0.01	0.66	<0.01	2.63	2.38
631616	Drill Core	1.20	<0.01	0.79	<0.01	0.50	2.26
631617	Drill Core	0.26	<0.01	0.18	<0.01	0.38	2.47
631618	Drill Core	1.02	<0.01	0.67	<0.01	0.51	2.30
631619	Drill Core	0.77	<0.01	0.50	<0.01	0.50	2.35
631620	Rock	0.11	0.01	0.02	<0.01	0.11	2.69
631621	Drill Core	1.44	<0.01	0.91	<0.01	1.25	2.21
631622	Drill Core	0.93	<0.01	0.57	<0.01	0.47	2.21
631623	Drill Core	0.63	<0.01	0.41	<0.01	0.59	2.40
631624	Drill Core	0.85	<0.01	0.57	<0.01	0.47	2.26
631625	Drill Core	1.24	<0.01	0.89	<0.01	1.03	2.30
631626	Drill Core	1.22	<0.01	0.80	<0.01	1.05	2.28
631627	Drill Core	0.13	<0.01	0.11	<0.01	0.55	2.44
631628	Drill Core	1.70	<0.01	1.00	<0.01	2.50	2.26
631629	Drill Core	1.85	<0.01	1.08	<0.01	1.94	2.25
631630	Rock Pulp	5.20	2.27	1.37	<0.01	5.50	N.A.
631631	Drill Core	1.76	<0.01	0.98	<0.01	2.33	2.23
631632	Drill Core	2.13	<0.01	1.20	<0.01	2.52	2.21
631633	Drill Core	0.29	<0.01	0.18	<0.01	1.79	2.54
631634	Drill Core	2.61	<0.01	1.46	<0.01	3.37	2.10
631635	Drill Core	2.38	<0.01	1.34	<0.01	10.84	2.44
631636	Drill Core	1.96	<0.01	1.06	<0.01	1.25	2.22
631637	Drill Core	1.13	<0.01	0.61	<0.01	0.71	2.28
631638	Drill Core	1.12	<0.01	0.62	<0.01	0.64	2.32
631639	Drill Core	1.78	<0.01	0.99	<0.01	1.58	2.25
631640	Drill Core	2.27	<0.01	1.25	<0.01	1.55	2.18



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: December 30, 2010

Page: 5 of 6 Part 1

CERTIFICATE OF ANALYSIS

WHI10000690.1

	Method Analyte Unit MDL	7TD.1	WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD
		Pb	Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg
		%	kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%
		0.02	0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01
631641	Drill Core		0.56	0.003	0.004	<0.02	0.59	4	0.011	<0.001	<0.01	1.09	<0.02	<0.01	0.002	<0.01	<0.01	1.23	0.46	0.005	0.28
631642	Drill Core		2.19	0.003	0.007	<0.02	0.17	2	0.010	<0.001	<0.01	1.63	<0.02	<0.01	<0.001	<0.01	<0.01	0.60	0.10	0.005	0.21
631643	Drill Core		1.26	0.002	0.004	<0.02	0.16	<2	0.008	<0.001	<0.01	0.86	<0.02	<0.01	<0.001	<0.01	<0.01	1.60	0.13	0.004	0.16
631644	Drill Core		0.93	<0.001	0.002	<0.02	0.05	<2	0.004	<0.001	<0.01	0.55	<0.02	<0.01	<0.001	<0.01	<0.01	0.65	0.11	0.004	0.10
631645	Drill Core		0.84	0.003	0.005	<0.02	0.26	2	0.008	<0.001	<0.01	0.91	<0.02	<0.01	<0.001	<0.01	<0.01	0.53	0.15	0.005	0.17
631646	Drill Core		2.58	<0.001	0.003	<0.02	0.12	<2	0.005	<0.001	<0.01	0.69	<0.02	<0.01	<0.001	<0.01	<0.01	1.41	0.34	0.005	0.10
631647	Drill Core		0.72	0.003	0.003	<0.02	0.13	<2	0.009	<0.001	<0.01	0.78	<0.02	<0.01	<0.001	<0.01	<0.01	1.41	0.17	0.005	0.16
631648	Drill Core		0.85	0.001	0.002	<0.02	0.11	<2	0.005	<0.001	<0.01	0.67	<0.02	<0.01	<0.001	<0.01	<0.01	1.91	0.67	0.004	0.12
631649	Drill Core		0.57	0.003	0.003	0.37	0.52	3	0.010	<0.001	<0.01	0.89	<0.02	<0.01	0.002	<0.01	<0.01	2.51	0.04	0.004	0.14
631650	Rock		0.31	<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	0.02	0.15	<0.02	<0.01	<0.001	<0.01	<0.01	20.99	0.03	<0.001	11.26
632101	Drill Core	13.01	0.61	<0.001	0.002	>10	21.61	2	<0.001	<0.001	0.02	0.28	<0.02	<0.01	0.107	<0.01	<0.01	12.91	0.01	<0.001	0.07
632102	Drill Core		2.01	<0.001	0.001	7.31	13.92	<2	<0.001	<0.001	0.03	0.79	<0.02	<0.01	0.066	<0.01	<0.01	20.31	<0.01	<0.001	0.06
632103	Drill Core		1.13	0.002	0.004	5.03	15.85	3	0.004	<0.001	0.02	1.86	<0.02	<0.01	0.054	<0.01	<0.01	7.33	0.05	0.002	0.07
632104	Drill Core	17.44	0.97	<0.001	0.003	>10	20.28	9	<0.001	<0.001	0.02	0.52	<0.02	<0.01	0.098	<0.01	<0.01	10.51	0.04	0.002	0.03
632105	Drill Core	14.40	1.30	<0.001	0.003	>10	19.92	7	<0.001	<0.001	0.02	0.20	<0.02	<0.01	0.095	<0.01	<0.01	12.69	0.04	0.001	0.03
632106	Drill Core	14.95	1.19	<0.001	0.003	>10	16.94	6	<0.001	<0.001	0.02	0.34	<0.02	<0.01	0.092	<0.01	<0.01	11.62	0.03	<0.001	0.03
632107	Drill Core	15.80	1.56	<0.001	0.002	>10	18.84	8	<0.001	<0.001	0.02	0.13	<0.02	<0.01	0.101	<0.01	<0.01	11.77	0.03	0.002	0.02
632108	Drill Core	13.49	0.61	<0.001	0.004	>10	18.36	12	<0.001	<0.001	0.02	0.18	<0.02	<0.01	0.103	<0.01	<0.01	13.40	0.03	0.002	0.02
632109	Drill Core	16.14	1.69	<0.001	0.002	>10	19.37	9	<0.001	<0.001	0.02	0.14	<0.02	<0.01	0.106	<0.01	<0.01	13.09	0.04	0.003	0.02
632110	Rock		0.41	<0.001	<0.001	0.05	0.05	<2	<0.001	<0.001	0.02	0.10	<0.02	0.01	<0.001	<0.01	<0.01	22.98	0.03	<0.001	11.91
632111	Drill Core	17.74	1.26	<0.001	0.003	>10	19.36	10	<0.001	<0.001	0.02	0.41	<0.02	<0.01	0.099	<0.01	<0.01	10.95	0.03	<0.001	0.04
632112	Drill Core	9.89	1.54	<0.001	0.003	>10	25.77	6	0.001	<0.001	0.01	3.68	<0.02	<0.01	0.113	<0.01	<0.01	3.11	0.04	0.003	0.02
632113	Drill Core		1.60	0.002	0.005	4.22	19.02	5	0.006	<0.001	0.02	4.04	<0.02	<0.01	0.053	<0.01	<0.01	4.95	0.04	0.004	0.09
632114	Drill Core		0.63	0.001	0.008	4.47	26.57	5	0.004	<0.001	0.03	3.34	<0.02	<0.01	0.066	<0.01	<0.01	0.76	0.05	0.003	0.05
632115	Drill Core		0.45	0.005	0.016	3.62	27.37	10	0.014	<0.001	0.02	5.77	<0.02	<0.01	0.074	<0.01	<0.01	4.69	0.06	0.004	0.13
632116	Drill Core		2.26	0.005	0.004	0.20	0.12	<2	0.013	<0.001	0.01	4.64	<0.02	<0.01	<0.001	<0.01	<0.01	5.68	0.16	0.004	0.16
632117	Drill Core		1.71	0.003	0.002	0.22	0.60	<2	0.010	<0.001	0.02	1.12	<0.02	<0.01	0.003	<0.01	<0.01	8.90	0.15	0.004	0.16
632118	Drill Core		2.23	<0.001	0.004	4.36	3.63	4	0.003	<0.001	0.02	0.79	<0.02	0.01	0.017	<0.01	<0.01	18.02	0.03	0.002	0.05
632119	Drill Core		3.18	0.002	0.005	0.07	0.62	<2	0.005	<0.001	<0.01	2.53	<0.02	<0.01	0.002	<0.01	<0.01	2.01	0.23	0.003	0.06
632120	Rock Pulp		0.06	<0.001	0.483	1.45	2.99	17	<0.001	<0.001	0.43	2.63	<0.02	0.02	0.018	<0.01	<0.01	4.92	0.02	0.001	0.32



Acme Analytical Laboratories (Vancouver) Ltd.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client:

Selwyn Resources Ltd.

Suite 700 - 509 Richards Street

Vancouver BC V6B 2Z6 Canada

Project:

Selwyn Project

Report Date:

December 30, 2010

Page:

5 of 6

Part 2

CERTIFICATE OF ANALYSIS

WHI10000690.1

	Method Analyte Unit MDL	7TD	7TD	7TD	7TD	7TD	G8SG
		Al	Na	K	W	S	SG
		%	%	%	%	%	
		0.01	0.01	0.01	0.01	0.05	0
631641	Drill Core	2.30	<0.01	1.28	<0.01	1.44	2.20
631642	Drill Core	1.77	<0.01	1.01	<0.01	1.91	2.20
631643	Drill Core	1.37	<0.01	0.80	<0.01	0.85	2.19
631644	Drill Core	0.86	<0.01	0.50	<0.01	0.39	2.38
631645	Drill Core	1.47	<0.01	0.83	<0.01	0.94	2.23
631646	Drill Core	0.93	<0.01	0.52	<0.01	0.62	2.35
631647	Drill Core	1.61	<0.01	0.96	<0.01	0.83	2.26
631648	Drill Core	1.10	<0.01	0.64	<0.01	0.62	2.36
631649	Drill Core	1.33	<0.01	0.77	<0.01	1.24	2.21
631650	Rock	0.07	<0.01	0.03	<0.01	<0.05	2.66
632101	Drill Core	0.02	<0.01	0.02	<0.01	12.06	3.16
632102	Drill Core	0.02	<0.01	0.03	<0.01	9.18	2.98
632103	Drill Core	0.50	<0.01	0.30	<0.01	11.14	2.74
632104	Drill Core	0.05	<0.01	0.03	<0.01	13.49	3.27
632105	Drill Core	0.06	<0.01	0.04	<0.01	12.86	3.01
632106	Drill Core	0.02	<0.01	0.02	<0.01	9.48	3.18
632107	Drill Core	0.02	<0.01	0.01	<0.01	9.67	3.17
632108	Drill Core	0.05	<0.01	0.02	<0.01	11.56	3.12
632109	Drill Core	0.03	<0.01	0.01	<0.01	12.31	3.20
632110	Rock	0.10	<0.01	0.02	<0.01	0.20	2.65
632111	Drill Core	0.10	<0.01	0.05	<0.01	12.89	3.16
632112	Drill Core	0.12	<0.01	0.06	<0.01	18.12	3.17
632113	Drill Core	0.56	<0.01	0.34	<0.01	14.35	2.84
632114	Drill Core	0.36	<0.01	0.21	<0.01	16.97	2.91
632115	Drill Core	1.07	<0.01	0.65	<0.01	20.57	2.86
632116	Drill Core	1.65	<0.01	1.11	<0.01	5.38	2.34
632117	Drill Core	1.31	<0.01	0.84	<0.01	1.54	2.31
632118	Drill Core	0.30	<0.01	0.17	<0.01	3.45	2.57
632119	Drill Core	0.42	<0.01	0.25	<0.01	3.02	2.41
632120	Rock Pulp	4.26	1.75	1.29	<0.01	3.37	N.A.



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**

Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: December 30, 2010

Page: 6 of 6 Part 1

CERTIFICATE OF ANALYSIS

WHI10000690.1

	Method Analyte Unit MDL	7TD.1	WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD
		Pb	Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr
		%	kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%
		0.02	0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.01
632121	Drill Core		1.76	0.004	0.013	0.18	0.46	<2	0.008	<0.001	0.03	2.47	<0.02	<0.01	0.002	<0.01	<0.01	15.65	0.55	0.004
632122	Drill Core		1.88	0.002	0.005	<0.02	0.03	<2	0.004	<0.001	0.05	1.21	<0.02	0.01	<0.001	<0.01	<0.01	28.37	0.19	0.001
632123	Drill Core		1.76	0.006	0.010	0.21	0.23	2	0.010	<0.001	0.03	1.97	<0.02	0.01	<0.001	<0.01	<0.01	23.90	0.38	0.005
632124	Drill Core		1.58	0.005	0.015	0.41	1.91	6	0.010	<0.001	0.03	2.36	<0.02	0.01	0.007	<0.01	<0.01	21.14	0.39	0.005
632125	Drill Core		1.59	0.004	0.009	0.09	0.53	<2	0.008	<0.001	0.02	1.14	<0.02	0.01	0.002	<0.01	<0.01	20.80	0.51	0.004
632126	Drill Core		2.45	0.003	0.006	<0.02	0.21	<2	0.007	<0.001	0.01	0.46	<0.02	<0.01	<0.001	<0.01	<0.01	8.90	0.33	0.003
632127	Drill Core		2.66	0.003	0.017	0.15	0.42	2	0.009	<0.001	0.01	5.46	<0.02	<0.01	0.001	<0.01	<0.01	7.90	0.28	0.005
632128	Drill Core		2.17	0.008	0.018	0.07	0.82	3	0.018	<0.001	0.01	1.67	<0.02	<0.01	0.003	<0.01	<0.01	4.26	0.26	0.006
632129	Drill Core		1.76	0.011	0.017	0.24	0.92	3	0.025	<0.001	<0.01	3.26	<0.02	<0.01	0.004	<0.01	<0.01	2.24	0.55	0.008
632130	Drill Core		0.71	0.002	0.019	0.18	0.18	4	0.025	<0.001	<0.01	3.10	<0.02	<0.01	<0.001	<0.01	<0.01	9.31	3.10	0.015
632131	Drill Core		0.69	0.001	0.014	0.16	0.18	3	0.026	<0.001	<0.01	1.77	<0.02	0.01	<0.001	<0.01	<0.01	9.91	3.32	0.020
632132	Drill Core		1.97	<0.001	0.002	<0.02	<0.01	<2	0.003	<0.001	0.03	2.26	<0.02	0.01	<0.001	<0.01	<0.01	20.24	0.05	0.004
632133	Drill Core		3.14	0.001	0.002	<0.02	<0.01	<2	0.006	<0.001	0.04	2.16	<0.02	0.02	<0.001	<0.01	<0.01	24.61	0.17	0.004



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: December 30, 2010

Page: 6 of 6 **Part** 2

CERTIFICATE OF ANALYSIS

WHI10000690.1

	Method Analyte Unit MDL	7TD	7TD	7TD	7TD	7TD	G8SG
		Al	Na	K	W	S	SG
		%	%	%	%	%	
		0.01	0.01	0.01	0.01	0.05	0
632121	Drill Core	0.54	<0.01	0.32	<0.01	3.14	2.31
632122	Drill Core	0.12	<0.01	0.09	<0.01	1.44	2.42
632123	Drill Core	0.85	<0.01	0.49	<0.01	2.58	2.25
632124	Drill Core	0.90	<0.01	0.52	<0.01	3.85	2.30
632125	Drill Core	0.73	<0.01	0.41	<0.01	1.70	2.25
632126	Drill Core	0.47	<0.01	0.27	<0.01	0.48	2.30
632127	Drill Core	0.58	<0.01	0.33	<0.01	6.63	2.44
632128	Drill Core	1.25	<0.01	0.73	<0.01	2.22	2.02
632129	Drill Core	1.65	<0.01	0.98	<0.01	4.23	1.98
632130	Drill Core	1.99	<0.01	1.35	<0.01	3.67	1.88
632131	Drill Core	2.08	<0.01	1.39	<0.01	2.14	1.82
632132	Drill Core	3.00	<0.01	0.89	<0.01	2.70	2.58
632133	Drill Core	2.96	<0.01	0.97	<0.01	2.57	2.48



Acme Analytical Laboratories (Vancouver) Ltd.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: **Selwyn Resources Ltd.**

Suite 700 - 509 Richards Street

Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: December 30, 2010

Page: 1 of 3 Part 1

QUALITY CONTROL REPORT

WHI10000690.1

	Method Analyte Unit MDL	7TD.1	WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	
		Pb	Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg
		%	kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%
		0.02	0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01
Pulp Duplicates																					
631563	Drill Core	2.66	0.003	0.004	0.12	0.89	2	0.012	<0.001	<0.01	1.14	<0.02	<0.01	0.005	<0.01	<0.01	1.04	0.23	0.004	0.14	
REP 631563	QC	0.004	0.004	0.13	0.91	3	0.012	<0.001	<0.01	1.16	<0.02	<0.01	0.005	<0.01	<0.01	1.06	0.24	0.004	0.15		
631583	Drill Core	2.22	0.002	0.004	1.20	5.67	<2	0.007	<0.001	0.02	2.99	<0.02	<0.01	0.015	<0.01	<0.01	4.76	0.09	0.003	0.12	
REP 631583	QC	0.001	0.004	1.24	5.75	<2	0.007	<0.001	0.02	3.05	<0.02	<0.01	0.017	<0.01	<0.01	4.72	0.10	0.003	0.13		
631595	Drill Core	11.90	1.42	<0.001	0.003	>10	18.45	4	0.002	<0.001	0.03	1.90	<0.02	<0.01	0.086	<0.01	<0.01	11.09	0.03	<0.001	0.05
REP 631595	QC	11.84																			
631608	Drill Core	1.04	<0.001	0.009	<0.02	0.24	<2	0.015	<0.001	<0.01	0.94	<0.02	<0.01	<0.001	<0.01	<0.01	5.55	1.88	0.007	0.28	
REP 631608	QC	<0.001	0.009	<0.02	0.24	<2	0.014	<0.001	<0.01	0.96	<0.02	<0.01	<0.001	<0.01	<0.01	5.61	1.89	0.007	0.28		
631648	Drill Core	0.85	0.001	0.002	<0.02	0.11	<2	0.005	<0.001	<0.01	0.67	<0.02	<0.01	<0.001	<0.01	<0.01	1.91	0.67	0.004	0.12	
REP 631648	QC	<0.001	0.002	<0.02	0.11	<2	0.005	<0.001	<0.01	0.68	<0.02	<0.01	<0.001	<0.01	<0.01	1.88	0.66	0.004	0.11		
632104	Drill Core	17.44	0.97	<0.001	0.003	>10	20.28	9	<0.001	<0.001	0.02	0.52	<0.02	<0.01	0.098	<0.01	<0.01	10.51	0.04	0.002	0.03
REP 632104	QC	17.10																			
632112	Drill Core	9.89	1.54	<0.001	0.003	>10	25.77	6	0.001	<0.001	0.01	3.68	<0.02	<0.01	0.113	<0.01	<0.01	3.11	0.04	0.003	0.02
REP 632112	QC	9.84																			
632117	Drill Core	1.71	0.003	0.002	0.22	0.60	<2	0.010	<0.001	0.02	1.12	<0.02	<0.01	0.003	<0.01	<0.01	8.90	0.15	0.004	0.16	
REP 632117	QC	0.003	0.003	0.22	0.60	<2	0.010	<0.001	0.02	1.12	<0.02	<0.01	0.002	<0.01	<0.01	8.88	0.15	0.003	0.16		
Core Reject Duplicates																					
631566	Drill Core	2.60	<0.001	0.003	0.99	3.23	<2	0.004	<0.001	0.05	1.14	<0.02	0.02	0.018	<0.01	<0.01	27.70	0.06	0.002	0.20	
DUP 631566	QC	<0.001	0.003	0.93	3.09	<2	0.004	<0.001	0.05	1.11	<0.02	0.02	0.018	<0.01	<0.01	27.90	0.06	0.002	0.20		
631601	Drill Core	1.01	<0.001	0.008	0.08	0.11	<2	0.014	<0.001	<0.01	1.70	<0.02	<0.01	<0.001	<0.01	<0.01	5.39	1.96	0.011	0.78	
DUP 631601	QC	<0.001	0.007	0.07	0.11	<2	0.014	<0.001	<0.01	1.67	<0.02	<0.01	<0.001	<0.01	<0.01	5.28	1.91	0.009	0.77		
631636	Drill Core	1.81	0.002	0.005	0.03	0.40	<2	0.010	<0.001	<0.01	1.02	<0.02	<0.01	0.001	<0.01	<0.01	2.79	0.87	0.006	0.27	
DUP 631636	QC	0.001	0.005	0.03	0.37	<2	0.009	<0.001	<0.01	1.07	<0.02	<0.01	0.001	<0.01	<0.01	2.72	0.84	0.006	0.27		
632121	Drill Core	1.76	0.004	0.013	0.18	0.46	<2	0.008	<0.001	0.03	2.47	<0.02	<0.01	0.002	<0.01	<0.01	15.65	0.55	0.004	0.10	
DUP 632121	QC	0.004	0.012	0.08	0.44	<2	0.008	<0.001	0.03	1.65	<0.02	<0.01	0.002	<0.01	<0.01	14.44	0.61	0.004	0.09		
Reference Materials																					
STD CCU-1C	Standard	0.42																			
STD CCU-1C	Standard	0.38																			



Acme Analytical Laboratories (Vancouver) Ltd.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: Selwyn Resources Ltd.

Suite 700 - 509 Richards Street

Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: December 30, 2010

Page: 1 of 3 **Part** 2

QUALITY CONTROL REPORT

WHI10000690.1

Method		7TD	7TD	7TD	7TD	7TD	G8SG
Analyte		Al	Na	K	W	S	SG
Unit		%	%	%	%	%	
MDL		0.01	0.01	0.01	0.01	0.05	0
Pulp Duplicates							
631563	Drill Core	1.64	<0.01	0.98	<0.01	1.67	2.16
REP 631563	QC	1.68	<0.01	1.00	<0.01	1.73	
631583	Drill Core	1.04	<0.01	0.61	<0.01	7.09	2.42
REP 631583	QC	1.05	<0.01	0.62	<0.01	7.19	
631595	Drill Core	0.20	<0.01	0.11	<0.01	13.00	3.11
REP 631595	QC						
631608	Drill Core	2.31	<0.01	1.33	<0.01	1.14	2.07
REP 631608	QC	2.34	<0.01	1.35	<0.01	1.14	
631648	Drill Core	1.10	<0.01	0.64	<0.01	0.62	2.36
REP 631648	QC	1.09	<0.01	0.63	<0.01	0.61	
632104	Drill Core	0.05	<0.01	0.03	<0.01	13.49	3.27
REP 632104	QC						
632112	Drill Core	0.12	<0.01	0.06	<0.01	18.12	3.17
REP 632112	QC						
632117	Drill Core	1.31	<0.01	0.84	<0.01	1.54	2.31
REP 632117	QC	1.30	<0.01	0.83	<0.01	1.53	
Core Reject Duplicates							
631566	Drill Core	1.01	<0.01	0.53	<0.01	3.15	2.55
DUP 631566	QC	1.01	<0.01	0.52	<0.01	3.03	2.56
631601	Drill Core	3.62	<0.01	2.35	<0.01	1.80	2.12
DUP 631601	QC	3.55	<0.01	2.30	<0.01	1.79	2.08
631636	Drill Core	1.96	<0.01	1.06	<0.01	1.25	2.22
DUP 631636	QC	1.95	<0.01	1.06	<0.01	1.23	2.21
632121	Drill Core	0.54	<0.01	0.32	<0.01	3.14	2.31
DUP 632121	QC	0.54	<0.01	0.30	<0.01	2.01	2.35
Reference Materials							
STD CCU-1C	Standard						
STD CCU-1C	Standard						



Acme Analytical Laboratories (Vancouver) Ltd.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: Selwyn Resources Ltd.

Suite 700 - 509 Richards Street

Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: December 30, 2010

Page: 2 of 3 Part 1

QUALITY CONTROL REPORT

WHI10000690.1

		7TD.1	WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD
		Pb	Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg
		%	kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%
		0.02	0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01
STD CCU-1C	Standard	0.41																			
STD CZN-3	Standard	0.10																			
STD CZN-3	Standard	0.11																			
STD CZN-3	Standard	0.04																			
STD OREAS131A	Standard			<0.001	0.032	1.71	2.90	31	0.003	0.002	0.17	5.88	<0.02	<0.01	0.008	<0.01	<0.01	5.42	0.06	0.003	3.10
STD OREAS131A	Standard			<0.001	0.033	1.76	2.87	31	0.002	0.002	0.17	5.91	<0.02	<0.01	0.008	<0.01	<0.01	5.38	0.05	0.002	3.20
STD OREAS131A	Standard			<0.001	0.033	1.79	2.94	32	0.003	0.002	0.17	5.93	<0.02	<0.01	0.008	<0.01	<0.01	5.48	0.05	0.002	3.20
STD OREAS131A	Standard			<0.001	0.033	1.75	2.94	31	0.003	0.002	0.18	5.90	<0.02	<0.01	0.008	<0.01	<0.01	5.41	0.07	0.002	3.16
STD OREAS131A	Standard			<0.001	0.032	1.71	2.88	31	0.003	0.002	0.18	5.93	<0.02	<0.01	0.008	<0.01	<0.01	5.45	0.05	0.003	3.17
STD OREAS131A	Standard			<0.001	0.032	1.72	2.90	31	0.003	0.002	0.17	5.95	<0.02	<0.01	0.008	<0.01	<0.01	5.46	0.06	0.003	3.13
STD OREAS131A	Standard			<0.001	0.033	1.80	2.89	31	0.003	0.002	0.17	5.80	<0.02	<0.01	0.008	<0.01	<0.01	5.36	0.06	0.002	3.15
STD OREAS131A	Standard			<0.001	0.036	1.77	2.95	31	0.002	0.002	0.17	5.81	<0.02	<0.01	0.008	<0.01	<0.01	5.32	0.06	0.002	3.16
STD PTC-1A	Standard	0.04																			
STD PTC-1A	Standard	0.06																			
STD PTC-1A	Standard	0.04																			
STD R4T	Standard			0.064	0.509	1.55	3.45	89	0.353	0.041	0.09	24.37	<0.02	0.02	0.019	0.01	<0.01	2.18	0.05	0.020	1.41
STD R4T	Standard			0.064	0.527	1.60	3.50	90	0.360	0.044	0.09	24.36	<0.02	0.02	0.018	0.01	<0.01	2.23	0.05	0.019	1.45
STD R4T	Standard			0.066	0.516	1.60	3.49	88	0.359	0.043	0.09	24.47	<0.02	0.02	0.019	0.02	<0.01	2.21	0.04	0.019	1.44
STD R4T	Standard			0.064	0.503	1.55	3.43	86	0.352	0.041	0.09	23.82	<0.02	0.02	0.019	0.02	<0.01	2.16	0.06	0.018	1.40
STD R4T	Standard			0.064	0.516	1.54	3.40	86	0.353	0.041	0.09	24.39	<0.02	0.02	0.019	0.02	<0.01	2.20	0.05	0.019	1.42
STD R4T	Standard			0.065	0.514	1.57	3.46	89	0.355	0.041	0.09	24.68	<0.02	0.02	0.019	0.02	<0.01	2.18	0.05	0.019	1.44
STD R4T	Standard			0.064	0.505	1.57	3.44	87	0.352	0.041	0.09	23.92	<0.02	0.02	0.018	0.01	<0.01	2.17	0.04	0.018	1.41
STD R4T	Standard			0.064	0.509	1.57	3.49	88	0.356	0.041	0.09	24.00	<0.02	0.02	0.018	0.02	<0.01	2.20	0.05	0.015	1.42
STD SARM 71	Standard	<0.02																			
STD SARM 71	Standard	<0.02																			
STD SARM 71	Standard	<0.02																			
STD SU-1B	Standard			<0.001	1.232	<0.02	0.02	6	2.004	0.069	0.07	26.05	<0.02	0.03	<0.001	<0.01	<0.01	2.27	0.08	0.032	1.81
STD SU-1B	Standard			<0.001	1.233	<0.02	0.02	7	2.033	0.068	0.07	25.28	<0.02	0.03	<0.001	<0.01	<0.01	2.24	0.06	0.034	1.81
STD SU-1B	Standard			<0.001	1.180	<0.02	0.03	7	2.002	0.069	0.07	25.51	<0.02	0.03	<0.001	<0.01	<0.01	2.23	0.06	0.033	1.82



Acme Analytical Laboratories (Vancouver) Ltd.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: **Selwyn Resources Ltd.**

Suite 700 - 509 Richards Street

Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: December 30, 2010

Page: 2 of 3 **Part** 2

QUALITY CONTROL REPORT

WHI10000690.1

		7TD Al %	7TD Na %	7TD K %	7TD W %	7TD S %	G8SG SG 0
STD CCU-1C	Standard						
STD CZN-3	Standard						
STD CZN-3	Standard						
STD CZN-3	Standard						
STD OREAS131A	Standard	4.61	0.15	3.46	<0.01	4.83	
STD OREAS131A	Standard	4.76	0.15	3.28	<0.01	5.28	
STD OREAS131A	Standard	4.76	0.16	3.39	<0.01	5.02	
STD OREAS131A	Standard	4.70	0.16	3.41	<0.01	4.96	
STD OREAS131A	Standard	4.62	0.16	3.29	<0.01	4.87	
STD OREAS131A	Standard	4.58	0.15	3.45	<0.01	4.88	
STD OREAS131A	Standard	4.64	0.15	3.21	<0.01	5.01	
STD OREAS131A	Standard	4.69	0.15	3.44	<0.01	4.86	
STD PTC-1A	Standard						
STD PTC-1A	Standard						
STD PTC-1A	Standard						
STD R4T	Standard	3.90	0.94	1.20	<0.01	11.73	
STD R4T	Standard	4.06	0.93	1.20	<0.01	14.11	
STD R4T	Standard	4.05	0.93	1.19	<0.01	12.26	
STD R4T	Standard	3.93	0.90	1.16	<0.01	12.66	
STD R4T	Standard	3.98	0.95	1.19	<0.01	12.38	
STD R4T	Standard	3.93	0.94	1.22	<0.01	11.77	
STD R4T	Standard	3.97	0.92	1.18	<0.01	12.77	
STD R4T	Standard	3.98	0.91	1.18	<0.01	14.11	
STD SARM 71	Standard						
STD SARM 71	Standard						
STD SARM 71	Standard						
STD SU-1B	Standard	4.43	1.78	0.65	<0.01	8.83	
STD SU-1B	Standard	4.46	1.73	0.63	<0.01	9.22	
STD SU-1B	Standard	4.48	1.74	0.63	<0.01	8.78	



Acme Analytical Laboratories (Vancouver) Ltd.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: Selwyn Resources Ltd.

Suite 700 - 509 Richards Street

Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: December 30, 2010

Page: 3 of 3 Part 1

QUALITY CONTROL REPORT

WHI10000690.1

		7TD.1	WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD
		Pb	Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg
		%	kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%
		0.02	0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.01	0.01
STD SU-1B	Standard			<0.001	1.166	<0.02	0.03	6	1.964	0.067	0.07	25.18	<0.02	0.03	<0.001	<0.01	<0.01	2.21	0.08	0.030	1.78
STD SU-1B	Standard			<0.001	1.221	<0.02	0.03	7	1.982	0.068	0.07	25.79	<0.02	0.03	<0.001	<0.01	<0.01	2.26	0.07	0.032	1.82
STD SU-1B	Standard			<0.001	1.209	<0.02	0.03	7	1.994	0.069	0.07	25.93	<0.02	0.03	<0.001	<0.01	<0.01	2.24	0.08	0.033	1.83
STD SU-1B	Standard			<0.001	1.165	<0.02	0.03	7	1.946	0.067	0.07	24.95	<0.02	0.03	<0.001	<0.01	<0.01	2.22	0.06	0.031	1.80
STD SU-1B	Standard			<0.001	1.189	<0.02	0.03	7	1.976	0.066	0.07	25.07	<0.02	0.03	<0.001	<0.01	<0.01	2.23	0.06	0.027	1.80
STD R4T Expected				0.062	0.502	1.518	3.376	86	0.339	0.039	0.086	24.07	0.0087	0.0185	0.018	0.0138	0.0018	2.166	0.045	0.018	1.384
STD OREAS131A Expected				0.001	0.0322	1.72	2.83	30.9	0.0027	0.0023	0.1722	5.8166	0.0082	0.0028	0.0081	0.0047	0.001	5.286	0.0536	0.0025	3.1182
STD SU-1B Expected				0.0004	1.185	0.0058	0.0235	6.4	1.97	0.0672	0.0703	25.54	0.00025	0.03	0.0003	0.00002	0.0003	2.21	0.06	0.032	1.79
STD CZN-3 Expected		0.113																			
STD CCU-1C Expected		0.34																			
STD PTC-1A Expected		0.05																			
BLK	Blank			<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	<0.01	<0.01	<0.02	<0.01	<0.001	<0.01	<0.01	<0.01	<0.01	<0.001	<0.01
BLK	Blank			<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	<0.01	<0.01	<0.02	<0.01	<0.001	<0.01	<0.01	<0.01	<0.01	<0.001	<0.01
BLK	Blank			<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	<0.01	<0.01	<0.02	<0.01	<0.001	<0.01	<0.01	<0.01	<0.01	<0.001	<0.01
BLK	Blank			<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	<0.01	<0.01	<0.02	<0.01	<0.001	<0.01	<0.01	<0.01	<0.01	<0.001	<0.01
BLK	Blank			<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	<0.01	<0.01	<0.02	<0.01	<0.001	<0.01	<0.01	<0.01	<0.01	<0.001	<0.01
BLK	Blank			<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	<0.01	<0.01	<0.02	<0.01	<0.001	<0.01	<0.01	<0.01	<0.01	<0.001	<0.01
BLK	Blank			<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	<0.01	<0.01	<0.02	<0.01	<0.001	<0.01	<0.01	<0.01	<0.01	<0.001	<0.01
BLK	Blank			<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	<0.01	<0.01	<0.02	<0.01	<0.001	<0.01	<0.01	<0.01	<0.01	<0.001	<0.01
BLK	Blank	<0.02																			
BLK	Blank	<0.02																			
BLK	Blank	<0.02																			
Prep Wash																					
G1	Prep Blank			<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	0.07	2.35	<0.02	0.07	<0.001	<0.01	<0.01	2.41	0.08	0.001	0.63
G1	Prep Blank			<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	0.07	2.37	<0.02	0.07	<0.001	<0.01	<0.01	2.36	0.08	0.001	0.63



Acme Analytical Laboratories (Vancouver) Ltd.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: **Selwyn Resources Ltd.**

Suite 700 - 509 Richards Street

Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: December 30, 2010

Page: 3 of 3 **Part** 2

QUALITY CONTROL REPORT

WHI10000690.1

		7TD Al %	7TD Na %	7TD K %	7TD W %	7TD S %	G8SG SG
		0.01	0.01	0.01	0.01	0.05	0
STD SU-1B	Standard	4.41	1.69	0.62	<0.01	8.74	
STD SU-1B	Standard	4.45	1.78	0.64	<0.01	8.96	
STD SU-1B	Standard	4.38	1.75	0.64	<0.01	8.41	
STD SU-1B	Standard	4.40	1.69	0.62	<0.01	9.07	
STD SU-1B	Standard	4.42	1.67	0.60	0.01	10.67	
STD R4T Expected		3.897	0.9	1.153	0.00016	12.9903	
STD OREAS131A Expected		4.6057	0.1501	3.1584	0.0005	4.8	
STD SU-1B Expected		4.39	1.662	0.6	0.0007	8.76	
STD CZN-3 Expected							
STD CCU-1C Expected							
STD PTC-1A Expected							
BLK	Blank	<0.01	<0.01	<0.01	<0.01	<0.05	
BLK	Blank	<0.01	<0.01	<0.01	<0.01	<0.05	
BLK	Blank	<0.01	<0.01	<0.01	<0.01	<0.05	
BLK	Blank	<0.01	<0.01	<0.01	<0.01	<0.05	
BLK	Blank	<0.01	<0.01	<0.01	<0.01	<0.05	
BLK	Blank	<0.01	<0.01	<0.01	<0.01	<0.05	
BLK	Blank	<0.01	<0.01	<0.01	<0.01	<0.05	
BLK	Blank	<0.01	<0.01	<0.01	<0.01	<0.05	
BLK	Blank						
BLK	Blank						
BLK	Blank						
Prep Wash							
G1	Prep Blank	7.97	2.71	3.09	<0.01	0.05	2.66
G1	Prep Blank	7.93	2.67	2.96	<0.01	<0.05	2.69



1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: Selwyn Resources Ltd.

Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Submitted By: Jason K. Dunning

Receiving Lab: Canada-Whitehorse

Received: December 13, 2010

Report Date: December 29, 2010

Page: 1 of 3

CERTIFICATE OF ANALYSIS

WHI10000689.1

CLIENT JOB INFORMATION

Project: Selwyn Project
Shipment ID:
P.O. Number 1156
Number of Samples: 56

SAMPLE DISPOSAL

STOR-PLP Store After 90 days Invoice for Storage
STOR-RJT Store After 90 days Invoice for Storage

Acme does not accept responsibility for samples left at the laboratory after 90 days without prior written instructions for sample storage or return.

Invoice To: Selwyn Resources Ltd.
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6
Canada

CC:

SAMPLE PREPARATION AND ANALYTICAL PROCEDURES

Method Code	Number of Samples	Code Description	Test Wgt (g)	Report Status	Lab
R200-250	55	Crush split and pulverize 250g drill core to 200 mesh			WHI
7TD2	56	4 Acid digestion ICP-ES analysis.	0.5	Completed	VAN
G812	56	Specific Gravity on Pulp		Completed	VAN
7TD.1	1	4 Acid digestion ICP-ES analysis	0.1	Completed	VAN

ADDITIONAL COMMENTS



This report supersedes all previous preliminary and final reports with this file number dated prior to the date on this certificate. Signature indicates final approval; preliminary reports are unsigned and should be used for reference only.

All results are considered the confidential property of the client. Acme assumes the liabilities for actual cost of analysis only.

“**” asterisk indicates that an analytical result could not be provided due to unusually high levels of interference from other elements.



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: December 29, 2010

Page: 2 of 3 Part 1

CERTIFICATE OF ANALYSIS

WHI10000689.1

Method Analyte Unit MDL		WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD
		Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg	Al
		kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%	%
		0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01	0.01
631701	Drill Core	1.14	<0.001	0.005	0.25	0.10	<2	0.010	<0.001	0.01	1.77	<0.02	0.01	<0.001	<0.01	<0.01	10.78	1.77	0.005	0.56	2.84
631702	Drill Core	0.83	<0.001	0.009	1.49	6.51	7	0.006	<0.001	0.01	4.06	<0.02	<0.01	0.024	<0.01	<0.01	5.39	0.12	0.003	0.27	1.21
631703	Drill Core	0.91	<0.001	0.004	0.12	<0.01	<2	0.012	<0.001	<0.01	1.33	<0.02	0.01	<0.001	<0.01	<0.01	7.96	2.14	0.009	0.60	3.14
631704	Drill Core	0.73	<0.001	0.002	0.03	0.23	<2	0.005	<0.001	<0.01	0.52	<0.02	<0.01	<0.001	<0.01	<0.01	2.06	0.64	0.003	0.11	1.20
631705	Drill Core	0.50	0.002	0.005	0.05	0.09	<2	0.009	<0.001	<0.01	0.86	<0.02	<0.01	<0.001	<0.01	<0.01	2.25	0.68	0.004	0.15	1.59
631706	Drill Core	0.53	0.001	0.002	0.03	<0.01	<2	0.007	<0.001	<0.01	0.44	<0.02	<0.01	<0.001	<0.01	<0.01	4.85	0.89	0.003	0.14	1.32
631707	Drill Core	1.50	0.003	0.012	4.05	10.92	4	0.008	<0.001	0.02	8.99	<0.02	<0.01	0.039	<0.01	<0.01	2.12	0.04	0.001	0.09	0.96
631708	Drill Core	1.15	0.001	0.006	5.31	5.75	2	0.004	<0.001	0.03	11.67	<0.02	<0.01	0.020	<0.01	<0.01	5.02	<0.01	0.002	0.05	0.30
631709	Drill Core	0.47	<0.001	0.001	0.10	0.31	<2	0.002	<0.001	0.06	1.14	<0.02	0.02	<0.001	<0.01	<0.01	32.29	0.02	<0.001	0.11	0.21
631710	Drill Core	0.54	0.003	0.007	1.15	6.99	3	0.008	<0.001	0.04	3.67	<0.02	<0.01	0.018	<0.01	<0.01	12.40	0.06	0.001	0.15	0.91
631711	Drill Core	0.55	0.003	0.005	1.28	5.28	<2	0.006	<0.001	0.05	2.78	<0.02	0.01	0.014	<0.01	<0.01	16.74	0.05	<0.001	0.14	0.73
631712	Drill Core	0.48	0.002	0.004	0.65	3.43	<2	0.004	<0.001	0.01	1.15	<0.02	<0.01	0.009	<0.01	<0.01	3.52	0.05	<0.001	0.08	0.55
631713	Drill Core	0.29	<0.001	0.002	0.03	0.06	<2	0.002	<0.001	0.04	2.21	<0.02	0.01	<0.001	<0.01	<0.01	28.75	0.02	<0.001	0.08	0.10
631714	Drill Core	0.60	0.006	0.003	0.04	1.16	<2	0.011	<0.001	<0.01	1.58	<0.02	<0.01	0.003	<0.01	<0.01	2.82	0.05	0.003	0.12	1.41
631715	Drill Core	2.00	0.004	0.012	1.88	8.89	3	0.009	<0.001	0.03	14.07	<0.02	<0.01	0.024	<0.01	<0.01	4.13	0.03	0.002	0.08	0.83
631716	Drill Core	0.62	0.004	0.020	2.99	16.39	5	0.007	<0.001	0.04	7.68	<0.02	<0.01	0.045	<0.01	<0.01	7.81	0.06	<0.001	0.09	0.70
631717	Drill Core	2.89	<0.001	<0.001	0.05	0.08	<2	<0.001	<0.001	0.07	0.67	<0.02	0.02	<0.001	<0.01	<0.01	33.11	0.02	<0.001	0.11	0.08
631718	Drill Core	0.65	<0.001	0.001	4.28	2.95	<2	<0.001	<0.001	0.04	0.37	<0.02	0.01	0.008	<0.01	<0.01	28.69	0.04	<0.001	0.07	0.20
631719	Drill Core	0.74	<0.001	0.002	1.49	4.02	<2	0.003	<0.001	0.02	1.71	<0.02	<0.01	0.011	<0.01	<0.01	5.31	0.05	0.002	0.07	0.59
631720	Rock	0.36	<0.001	<0.001	<0.02	<0.01	<2	0.002	<0.001	0.02	0.49	<0.02	<0.01	<0.001	<0.01	<0.01	19.58	0.03	0.002	11.26	0.46
631721	Drill Core	0.64	<0.001	<0.001	0.43	1.48	<2	0.001	<0.001	0.04	0.99	<0.02	0.02	0.005	<0.01	<0.01	31.71	0.03	<0.001	0.11	0.32
631722	Drill Core	0.59	0.002	0.003	1.39	7.70	<2	0.003	<0.001	0.05	2.78	<0.02	0.01	0.021	<0.01	<0.01	21.71	0.04	0.002	0.11	0.45
631723	Drill Core	0.98	0.001	0.003	0.83	1.46	<2	0.004	<0.001	0.02	8.62	<0.02	<0.01	0.004	<0.01	<0.01	3.25	0.04	0.003	0.06	0.54
631724	Drill Core	0.84	0.003	0.010	6.99	31.34	8	0.007	<0.001	0.02	5.91	<0.02	<0.01	0.072	<0.01	<0.01	1.48	0.07	0.002	0.07	0.70
631725	Drill Core	0.85	0.002	0.007	5.23	27.56	5	0.005	<0.001	0.01	4.23	<0.02	<0.01	0.062	<0.01	<0.01	1.99	0.06	0.002	0.05	0.54
631726	Drill Core	0.70	<0.001	0.003	2.52	19.07	<2	0.002	<0.001	0.02	3.08	<0.02	<0.01	0.049	<0.01	<0.01	6.75	0.02	<0.001	0.03	0.18
631727	Drill Core	1.37	0.002	0.004	3.38	8.82	2	0.006	<0.001	0.03	2.44	<0.02	<0.01	0.025	<0.01	<0.01	9.16	0.06	0.002	0.10	0.66
631728	Drill Core	0.86	0.001	0.002	0.57	1.88	<2	0.004	<0.001	0.04	0.93	<0.02	0.01	0.005	<0.01	<0.01	24.19	0.06	0.002	0.10	0.62
631729	Drill Core	1.56	0.002	0.006	2.52	6.14	3	0.007	<0.001	0.02	2.58	<0.02	<0.01	0.016	<0.01	<0.01	7.61	0.22	0.002	0.10	0.74
631730	Rock Pulp	0.06	<0.001	0.660	5.91	7.03	70	0.001	0.001	0.09	4.93	<0.02	0.02	0.019	0.01	<0.01	1.34	0.02	0.001	0.24	4.66



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: December 29, 2010

Page: 2 of 3 **Part** 2

CERTIFICATE OF ANALYSIS

WHI10000689.1

	Method Analyte Unit MDL	7TD	7TD	7TD	7TD	G8SG	7TD.1
		Na	K	W	S	SG	Pb
		%	%	%	%		%
		0.01	0.01	0.01	0.05	0	0.02
631701	Drill Core	0.01	1.61	<0.01	1.84	2.22	
631702	Drill Core	<0.01	0.76	<0.01	7.82	2.54	
631703	Drill Core	<0.01	1.67	<0.01	1.30	2.07	
631704	Drill Core	<0.01	0.72	<0.01	0.54	2.37	
631705	Drill Core	<0.01	0.84	<0.01	0.86	2.23	
631706	Drill Core	<0.01	0.72	<0.01	0.36	2.26	
631707	Drill Core	<0.01	0.51	<0.01	15.27	2.79	
631708	Drill Core	<0.01	0.14	<0.01	15.95	2.95	
631709	Drill Core	<0.01	0.09	<0.01	1.38	2.47	
631710	Drill Core	<0.01	0.43	<0.01	7.69	2.52	
631711	Drill Core	<0.01	0.32	<0.01	5.79	2.54	
631712	Drill Core	<0.01	0.26	<0.01	2.70	2.45	
631713	Drill Core	<0.01	0.04	<0.01	2.44	2.54	
631714	Drill Core	<0.01	0.80	<0.01	2.13	2.16	
631715	Drill Core	<0.01	0.49	<0.01	19.50	2.80	
631716	Drill Core	<0.01	0.42	<0.01	16.34	2.77	
631717	Drill Core	<0.01	0.03	<0.01	0.79	2.54	
631718	Drill Core	<0.01	0.10	<0.01	2.23	2.69	
631719	Drill Core	<0.01	0.34	<0.01	3.88	2.64	
631720	Rock	0.01	0.11	<0.01	0.14	2.67	
631721	Drill Core	<0.01	0.15	<0.01	1.75	2.55	
631722	Drill Core	<0.01	0.20	<0.01	6.70	2.70	
631723	Drill Core	<0.01	0.29	<0.01	10.02	2.75	
631724	Drill Core	<0.01	0.39	<0.01	21.16	3.32	
631725	Drill Core	<0.01	0.31	<0.01	17.51	3.04	
631726	Drill Core	<0.01	0.09	<0.01	12.15	2.95	
631727	Drill Core	<0.01	0.37	<0.01	7.73	2.67	
631728	Drill Core	<0.01	0.32	<0.01	2.21	2.50	
631729	Drill Core	<0.01	0.42	<0.01	6.32	2.56	
631730	Rock Pulp	2.30	1.36	<0.01	5.14	N.A.	



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**

Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: December 29, 2010

Page: 3 of 3 Part 1

CERTIFICATE OF ANALYSIS

WHI10000689.1

	Method Analyte Unit MDL	WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD
		Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg	Al
		kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%	%
		0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01	0.01
631731	Drill Core	1.96	0.006	0.019	1.22	2.25	4	0.015	<0.001	0.02	5.80	<0.02	<0.01	0.006	<0.01	<0.01	9.86	0.76	0.006	0.14	0.99
631732	Drill Core	1.80	0.002	0.003	2.35	7.23	3	0.006	<0.001	0.03	2.82	<0.02	<0.01	0.022	<0.01	<0.01	10.07	0.07	0.003	0.10	0.71
631733	Drill Core	1.09	<0.001	0.003	>10	21.75	6	0.002	<0.001	<0.01	0.85	<0.02	<0.01	0.081	<0.01	<0.01	0.61	0.02	0.001	0.02	0.21
631734	Drill Core	0.97	0.001	0.005	4.19	19.01	5	0.005	<0.001	0.02	4.55	<0.02	<0.01	0.044	<0.01	<0.01	7.63	0.03	0.001	0.05	0.34
631735	Drill Core	1.50	0.001	0.007	5.82	37.81	8	0.003	<0.001	0.02	2.21	<0.02	<0.01	0.095	<0.01	<0.01	1.85	0.04	0.001	0.03	0.27
631736	Drill Core	0.61	0.003	0.006	1.40	12.61	2	0.009	<0.001	0.02	3.08	<0.02	<0.01	0.034	<0.01	<0.01	3.65	0.11	0.003	0.13	1.24
631737	Drill Core	0.90	0.002	0.004	3.36	7.61	<2	0.006	<0.001	0.03	1.79	<0.02	<0.01	0.023	<0.01	<0.01	9.31	0.09	0.002	0.11	0.90
631738	Drill Core	0.48	0.001	0.002	0.29	0.04	<2	0.005	<0.001	0.02	1.79	<0.02	<0.01	<0.001	<0.01	<0.01	13.21	0.06	0.002	0.13	0.81
631739	Drill Core	3.15	<0.001	0.002	<0.02	<0.01	<2	0.002	<0.001	0.05	1.00	<0.02	0.02	<0.001	<0.01	<0.01	32.54	0.03	0.001	0.11	0.38
631740	Drill Core	0.49	<0.001	0.003	0.05	0.29	<2	0.005	<0.001	0.03	1.42	<0.02	<0.01	0.001	<0.01	<0.01	16.67	0.06	0.002	0.11	0.58
631741	Drill Core	0.55	0.001	0.003	0.04	0.12	<2	0.006	<0.001	0.03	1.20	<0.02	<0.01	<0.001	<0.01	<0.01	12.58	0.07	0.002	0.13	0.81
631742	Drill Core	0.84	<0.001	0.002	<0.02	<0.01	<2	0.004	<0.001	<0.01	0.44	<0.02	<0.01	<0.001	<0.01	<0.01	2.28	0.04	0.002	0.06	0.42
631743	Drill Core	1.60	<0.001	0.002	<0.02	<0.01	<2	0.003	<0.001	0.05	0.51	<0.02	0.02	<0.001	<0.01	<0.01	31.12	0.04	0.001	0.08	0.33
631744	Drill Core	0.65	<0.001	0.003	<0.02	<0.01	<2	0.004	<0.001	<0.01	0.84	<0.02	<0.01	<0.001	<0.01	<0.01	1.55	0.02	0.002	0.06	0.39
631745	Drill Core	1.63	0.001	0.003	0.35	0.07	<2	0.005	<0.001	0.04	0.73	<0.02	0.01	<0.001	<0.01	<0.01	24.85	0.07	0.002	0.11	0.60
631746	Drill Core	1.67	0.002	0.004	0.95	0.63	3	0.007	<0.001	0.01	1.23	<0.02	<0.01	0.002	<0.01	<0.01	3.06	0.25	0.003	0.08	0.57
631747	Drill Core	2.53	0.005	0.012	0.43	0.61	3	0.009	<0.001	0.02	1.11	<0.02	0.01	0.002	<0.01	<0.01	16.23	1.20	0.004	0.10	0.66
631748	Drill Core	1.95	0.004	0.007	0.12	0.63	<2	0.010	<0.001	0.01	0.72	<0.02	<0.01	0.002	<0.01	<0.01	10.11	0.28	0.004	0.09	0.68
631749	Drill Core	1.37	0.008	0.017	0.20	1.99	3	0.018	<0.001	<0.01	1.82	<0.02	<0.01	0.007	<0.01	<0.01	4.15	0.25	0.005	0.15	1.22
631750	Rock	0.35	<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	0.01	0.15	<0.02	<0.01	<0.001	<0.01	<0.01	21.64	0.03	<0.001	11.51	0.13
631751	Drill Core	1.90	0.009	0.016	0.06	0.38	<2	0.019	<0.001	<0.01	1.69	<0.02	<0.01	0.001	<0.01	<0.01	2.35	0.28	0.006	0.18	1.33
631752	Drill Core	1.99	<0.001	0.002	<0.02	<0.01	<2	0.004	<0.001	0.04	1.42	<0.02	0.02	<0.001	<0.01	<0.01	27.81	1.34	0.003	0.29	1.87
631753	Drill Core	1.19	0.010	0.018	<0.02	0.03	<2	0.036	0.001	0.01	3.36	0.02	<0.01	<0.001	<0.01	<0.01	3.09	0.21	0.018	0.49	4.34
631754	Drill Core	1.67	0.005	0.022	0.10	0.38	<2	0.015	<0.001	0.01	3.87	<0.02	<0.01	0.001	0.01	<0.01	6.19	0.22	0.007	0.21	1.50
631755	Drill Core	1.03	0.007	0.028	0.19	1.07	<2	0.019	<0.001	<0.01	4.87	<0.02	<0.01	0.004	<0.01	<0.01	4.11	0.22	0.005	0.21	1.44
631756	Drill Core	1.45	<0.001	0.002	<0.02	<0.01	<2	0.002	<0.001	0.04	1.65	<0.02	0.02	<0.001	<0.01	<0.01	26.39	0.05	0.003	0.38	2.31



Acme Analytical Laboratories (Vancouver) Ltd.
1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: Selwyn Resources Ltd.
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: December 29, 2010

Page: 3 of 3 **Part** 2

CERTIFICATE OF ANALYSIS

WHI10000689.1

	Method Analyte Unit MDL	7TD	7TD	7TD	7TD	G8SG	7TD.1
		Na	K	W	S	SG	Pb
		%	%	%	%		%
		0.01	0.01	0.01	0.05	0	0.02
631731	Drill Core	<0.01	0.50	<0.01	8.17	2.47	
631732	Drill Core	<0.01	0.36	<0.01	7.20	2.56	
631733	Drill Core	<0.01	0.10	<0.01	12.80	3.09	12.39
631734	Drill Core	0.04	0.16	<0.01	14.74	2.91	
631735	Drill Core	<0.01	0.12	<0.01	21.14	3.25	
631736	Drill Core	<0.01	0.72	<0.01	9.65	2.57	
631737	Drill Core	<0.01	0.52	<0.01	6.31	2.64	
631738	Drill Core	<0.01	0.43	<0.01	2.16	2.41	
631739	Drill Core	<0.01	0.19	<0.01	1.30	2.53	
631740	Drill Core	<0.01	0.33	<0.01	1.82	2.43	
631741	Drill Core	<0.01	0.48	<0.01	1.43	2.42	
631742	Drill Core	<0.01	0.24	<0.01	0.34	2.40	
631743	Drill Core	<0.01	0.17	<0.01	0.71	2.40	
631744	Drill Core	<0.01	0.22	<0.01	0.82	2.47	
631745	Drill Core	<0.01	0.33	<0.01	1.00	2.37	
631746	Drill Core	<0.01	0.33	<0.01	1.75	2.37	
631747	Drill Core	<0.01	0.36	<0.01	1.68	2.34	
631748	Drill Core	<0.01	0.38	<0.01	1.13	2.25	
631749	Drill Core	<0.01	0.70	<0.01	3.04	2.12	
631750	Rock	0.01	0.03	<0.01	0.12	2.71	
631751	Drill Core	<0.01	0.80	<0.01	2.05	2.07	
631752	Drill Core	<0.01	1.02	<0.01	1.68	2.51	
631753	Drill Core	<0.01	2.38	<0.01	3.80	1.70	
631754	Drill Core	<0.01	0.79	<0.01	4.54	2.22	
631755	Drill Core	<0.01	0.85	<0.01	5.75	2.22	
631756	Drill Core	<0.01	1.27	<0.01	1.97	2.64	



Acme Analytical Laboratories (Vancouver) Ltd.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: Selwyn Resources Ltd.

Suite 700 - 509 Richards Street

Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: December 29, 2010

Page: 1 of 2 Part 1

QUALITY CONTROL REPORT

WHI10000689.1

	Method Analyte Unit MDL	WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD
		Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg	Al
		kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%	%
		0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01	0.01
Pulp Duplicates																					
631714	Drill Core	0.60	0.006	0.003	0.04	1.16	<2	0.011	<0.001	<0.01	1.58	<0.02	<0.01	0.003	<0.01	<0.01	2.82	0.05	0.003	0.12	1.41
REP 631714	QC		0.006	0.003	0.04	1.16	<2	0.012	<0.001	<0.01	1.63	<0.02	<0.01	0.003	<0.01	<0.01	2.83	0.05	0.002	0.13	1.43
631733	Drill Core	1.09	<0.001	0.003	>10	21.75	6	0.002	<0.001	<0.01	0.85	<0.02	<0.01	0.081	<0.01	<0.01	0.61	0.02	0.001	0.02	0.21
REP 631733	QC																				
631739	Drill Core	3.15	<0.001	0.002	<0.02	<0.01	<2	0.002	<0.001	0.05	1.00	<0.02	0.02	<0.001	<0.01	<0.01	32.54	0.03	0.001	0.11	0.38
REP 631739	QC		<0.001	0.002	<0.02	<0.01	<2	0.002	<0.001	0.05	1.00	<0.02	0.02	<0.001	<0.01	<0.01	32.27	0.03	0.001	0.11	0.38
Core Reject Duplicates																					
631713	Drill Core	0.29	<0.001	0.002	0.03	0.06	<2	0.002	<0.001	0.04	2.21	<0.02	0.01	<0.001	<0.01	<0.01	28.75	0.02	<0.001	0.08	0.10
DUP 631713	QC		I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.	I.S.
631748	Drill Core	1.95	0.004	0.007	0.12	0.63	<2	0.010	<0.001	0.01	0.72	<0.02	<0.01	0.002	<0.01	<0.01	10.11	0.28	0.004	0.09	0.68
DUP 631748	QC		0.004	0.007	0.12	0.63	<2	0.010	<0.001	0.01	0.74	<0.02	<0.01	0.002	<0.01	<0.01	10.10	0.28	0.004	0.10	0.69
Reference Materials																					
STD CCU-1C	Standard																				
STD CZN-3	Standard																				
STD OREAS131A	Standard		<0.001	0.032	1.71	2.90	31	0.003	0.002	0.17	5.88	<0.02	<0.01	0.008	<0.01	<0.01	5.42	0.06	0.003	3.10	4.61
STD OREAS131A	Standard		<0.001	0.032	1.68	2.87	31	0.003	0.002	0.17	5.74	<0.02	<0.01	0.008	<0.01	<0.01	5.29	0.05	0.002	3.17	4.67
STD PTC-1A	Standard																				
STD R4T	Standard		0.064	0.509	1.55	3.45	89	0.353	0.041	0.09	24.37	<0.02	0.02	0.019	0.01	<0.01	2.18	0.05	0.020	1.41	3.90
STD R4T	Standard		0.062	0.504	1.54	3.37	87	0.348	0.040	0.09	23.85	<0.02	0.02	0.018	0.01	<0.01	2.20	0.05	0.019	1.42	3.96
STD SARM 71	Standard																				
STD SU-1B	Standard		<0.001	1.232	<0.02	0.02	6	2.004	0.069	0.07	26.05	<0.02	0.03	<0.001	<0.01	<0.01	2.27	0.08	0.032	1.81	4.43
STD SU-1B	Standard		<0.001	1.183	<0.02	0.03	8	1.959	0.066	0.07	25.19	<0.02	0.03	<0.001	<0.01	<0.01	2.25	0.06	0.031	1.82	4.43
STD R4T Expected			0.062	0.502	1.518	3.376	86	0.339	0.039	0.086	24.07	0.0087	0.0185	0.018	0.0138	0.0018	2.166	0.045	0.018	1.384	3.897
STD OREAS131A Expected			0.001	0.0322	1.72	2.83	30.9	0.0027	0.0023	0.1722	5.8166	0.0082	0.0028	0.0081	0.0047	0.001	5.286	0.0536	0.0025	3.1182	4.6057
STD SU-1B Expected			0.0004	1.185	0.0058	0.0235	6.4	1.97	0.0672	0.0703	25.54	0.00025	0.03	0.0003	0.00002	0.0003	2.21	0.06	0.032	1.79	4.39
STD CZN-3 Expected																					
STD CCU-1C Expected																					
STD PTC-1A Expected																					



Acme Analytical Laboratories (Vancouver) Ltd.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: **Selwyn Resources Ltd.**

Suite 700 - 509 Richards Street

Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: December 29, 2010

Page: 1 of 2 Part 2

QUALITY CONTROL REPORT

WHI10000689.1

Method		7TD	7TD	7TD	7TD	G8SG	7TD.1
Analyte		Na	K	W	S	SG	Pb
Unit		%	%	%	%		%
MDL		0.01	0.01	0.01	0.05	0	0.02
Pulp Duplicates							
631714	Drill Core	<0.01	0.80	<0.01	2.13	2.16	
REP 631714	QC	<0.01	0.82	<0.01	2.18		
631733	Drill Core	<0.01	0.10	<0.01	12.80	3.09	12.39
REP 631733	QC						12.48
631739	Drill Core	<0.01	0.19	<0.01	1.30	2.53	
REP 631739	QC	<0.01	0.19	<0.01	1.31		
Core Reject Duplicates							
631713	Drill Core	<0.01	0.04	<0.01	2.44	2.54	
DUP 631713	QC	I.S.	I.S.	I.S.	I.S.	2.57	
631748	Drill Core	<0.01	0.38	<0.01	1.13	2.25	
DUP 631748	QC	<0.01	0.39	<0.01	1.14	2.27	
Reference Materials							
STD CCU-1C	Standard						0.38
STD CZN-3	Standard						0.09
STD OREAS131A	Standard	0.15	3.46	<0.01	4.83		
STD OREAS131A	Standard	0.15	3.22	<0.01	4.56		
STD PTC-1A	Standard						0.05
STD R4T	Standard	0.94	1.20	<0.01	11.73		
STD R4T	Standard	0.92	1.19	<0.01	11.01		
STD SARF 71	Standard						<0.02
STD SU-1B	Standard	1.78	0.65	<0.01	8.83		
STD SU-1B	Standard	1.69	0.61	<0.01	7.99		
STD R4T Expected		0.9	1.153	0.00016	12.9903		
STD OREAS131A Expected		0.1501	3.1584	0.0005	4.8		
STD SU-1B Expected		1.662	0.6	0.0007	8.76		
STD CZN-3 Expected							0.113
STD CCU-1C Expected							0.34
STD PTC-1A Expected							0.05



Acme Analytical Laboratories (Vancouver) Ltd.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: **Selwyn Resources Ltd.**

Suite 700 - 509 Richards Street

Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: December 29, 2010

Page: 2 of 2 Part 1

QUALITY CONTROL REPORT

WHI10000689.1

		WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD
		Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg
		kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%
		0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01
BLK	Blank		<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	<0.01	<0.01	<0.02	<0.01	<0.001	<0.01	<0.01	<0.01	<0.01	<0.001	<0.01
BLK	Blank		<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	<0.01	<0.01	<0.02	<0.01	<0.001	<0.01	<0.01	<0.01	<0.01	<0.001	<0.01
BLK	Blank																			
Prep Wash																				
G1	Prep Blank		<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	0.07	2.33	<0.02	0.07	<0.001	<0.01	<0.01	2.38	0.07	<0.001	0.65
G1	Prep Blank		<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	0.07	2.36	<0.02	0.07	<0.001	<0.01	<0.01	2.38	0.07	<0.001	0.68



Acme Analytical Laboratories (Vancouver) Ltd.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: **Selwyn Resources Ltd.**

Suite 700 - 509 Richards Street

Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: December 29, 2010

Page: 2 of 2 **Part** 2

QUALITY CONTROL REPORT

WHI10000689.1

		7TD Na %	7TD K %	7TD W %	7TD S %	G8SG SG 0	7TD.1 Pb %
		0.01	0.01	0.01	0.05	0	0.02
BLK	Blank	<0.01	<0.01	<0.01	<0.05		
BLK	Blank	<0.01	<0.01	<0.01	<0.05		
BLK	Blank						<0.02
Prep Wash							
G1	Prep Blank	2.69	1.87	<0.01	<0.05	2.70	
G1	Prep Blank	2.71	1.84	<0.01	<0.05	2.69	



1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: Selwyn Resources Ltd.

Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Submitted By: Jason K. Dunning

Receiving Lab: Canada-Whitehorse

Received: December 06, 2010

Report Date: December 27, 2010

Page: 1 of 4

CERTIFICATE OF ANALYSIS

WHI10000678.1

CLIENT JOB INFORMATION

Project: Selwyn Project
Shipment ID:
P.O. Number 1127
Number of Samples: 76

SAMPLE DISPOSAL

STOR-PLP Store After 90 days Invoice for Storage
STOR-RJT Store After 90 days Invoice for Storage

Acme does not accept responsibility for samples left at the laboratory after 90 days without prior written instructions for sample storage or return.

Invoice To: Selwyn Resources Ltd.
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6
Canada

CC:

SAMPLE PREPARATION AND ANALYTICAL PROCEDURES

Method Code	Number of Samples	Code Description	Test Wgt (g)	Report Status	Lab
R200-250	74	Crush split and pulverize 250g drill core to 200 mesh			WHI
7TD2	76	4 Acid digestion ICP-ES analysis.	0.5	Completed	VAN
G812	76	Specific Gravity on Pulp		Completed	VAN
7TD.1	1	4 Acid digestion ICP-ES analysis	0.1	Completed	VAN

ADDITIONAL COMMENTS



This report supersedes all previous preliminary and final reports with this file number dated prior to the date on this certificate. Signature indicates final approval; preliminary reports are unsigned and should be used for reference only.

All results are considered the confidential property of the client. Acme assumes the liabilities for actual cost of analysis only.

“**” asterisk indicates that an analytical result could not be provided due to unusually high levels of interference from other elements.



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: December 27, 2010

Page: 2 of 4 Part 1

CERTIFICATE OF ANALYSIS

WHI10000678.1

	Method Analyte Unit MDL	WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD
		Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg	Al
		kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%	%
		0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01	0.01
632201	Drill Core	0.44	<0.001	0.012	0.27	6.79	6	0.005	<0.001	0.03	3.16	<0.02	0.02	0.021	<0.01	<0.01	17.20	0.20	0.003	0.24	0.92
632202	Drill Core	2.10	0.004	0.004	0.09	0.76	<2	0.012	<0.001	<0.01	1.10	<0.02	<0.01	0.003	<0.01	<0.01	1.34	0.49	0.004	0.16	1.70
632203	Drill Core	0.90	0.004	0.012	1.24	7.45	3	0.008	<0.001	0.01	6.16	<0.02	<0.01	0.035	<0.01	<0.01	0.66	0.03	0.002	0.07	0.86
632204	Drill Core	0.86	0.005	0.009	2.23	5.48	2	0.010	<0.001	<0.01	11.51	<0.02	<0.01	0.020	<0.01	<0.01	0.41	0.06	0.003	0.12	1.58
632205	Drill Core	0.91	0.004	0.009	1.07	7.11	2	0.008	<0.001	0.01	7.28	<0.02	<0.01	0.021	<0.01	<0.01	0.27	0.04	0.002	0.08	0.96
632206	Drill Core	1.34	0.002	0.010	2.58	7.88	3	0.005	<0.001	0.01	15.49	<0.02	<0.01	0.032	<0.01	<0.01	0.85	0.03	0.001	0.06	0.73
632207	Drill Core	1.07	0.004	0.015	2.70	15.91	4	0.011	<0.001	0.02	12.52	<0.02	<0.01	0.057	<0.01	<0.01	0.24	0.05	0.002	0.10	1.14
632208	Drill Core	0.97	0.004	0.004	0.45	1.99	<2	0.009	<0.001	0.01	4.50	<0.02	<0.01	0.006	<0.01	<0.01	0.75	0.03	0.002	0.09	0.92
632209	Drill Core	0.66	0.003	0.005	0.81	5.35	<2	0.008	<0.001	0.01	4.84	<0.02	<0.01	0.015	<0.01	<0.01	0.65	0.04	0.003	0.08	0.82
632210	Drill Core	0.55	0.005	0.009	0.76	8.88	2	0.012	<0.001	0.02	6.26	<0.02	<0.01	0.019	<0.01	<0.01	1.35	0.08	0.003	0.12	1.42
632211	Drill Core	0.66	0.006	0.009	1.00	8.44	2	0.013	<0.001	0.02	6.86	<0.02	<0.01	0.018	<0.01	<0.01	0.75	0.08	0.003	0.13	1.47
632212	Drill Core	1.34	0.003	0.006	4.14	10.45	2	0.006	<0.001	0.01	3.25	<0.02	<0.01	0.026	<0.01	<0.01	1.85	0.06	0.002	0.07	0.75
632213	Drill Core	1.16	<0.001	<0.001	0.80	0.10	<2	<0.001	<0.001	0.07	0.32	<0.02	0.02	<0.001	<0.01	<0.01	32.28	0.01	<0.001	0.08	0.07
632214	Drill Core	0.72	0.002	0.004	1.38	7.00	<2	0.006	<0.001	0.01	2.86	<0.02	<0.01	0.018	<0.01	<0.01	1.98	0.09	<0.001	0.07	0.62
632215	Drill Core	0.67	0.001	0.002	0.44	1.17	<2	0.004	<0.001	0.03	0.73	<0.02	<0.01	0.003	<0.01	<0.01	21.56	0.05	0.001	0.09	0.47
632216	Drill Core	0.84	0.001	0.002	0.49	1.91	<2	0.004	<0.001	0.01	0.82	<0.02	<0.01	0.005	<0.01	<0.01	7.71	0.03	0.001	0.06	0.44
632217	Drill Core	1.62	<0.001	<0.001	0.06	0.53	<2	0.002	<0.001	0.03	0.66	<0.02	0.01	0.001	<0.01	<0.01	18.99	0.02	<0.001	0.05	0.21
632218	Drill Core	1.55	<0.001	0.001	0.17	0.99	<2	0.003	<0.001	0.03	0.49	<0.02	0.01	0.002	<0.01	<0.01	25.87	0.02	<0.001	0.06	0.20
632219	Drill Core	1.34	0.001	0.003	0.17	0.83	<2	0.004	<0.001	0.02	0.96	<0.02	<0.01	0.002	<0.01	<0.01	14.77	0.03	<0.001	0.05	0.34
632220	Rock	0.39	<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	0.01	0.15	<0.02	<0.01	<0.001	<0.01	<0.01	20.83	0.03	<0.001	10.87	0.14
632221	Drill Core	2.26	0.002	0.002	0.26	1.33	<2	0.007	<0.001	0.01	0.82	<0.02	<0.01	0.004	<0.01	<0.01	3.88	0.05	0.002	0.06	0.62
632222	Drill Core	2.16	0.004	0.004	0.75	3.27	<2	0.010	<0.001	<0.01	1.31	<0.02	<0.01	0.009	<0.01	<0.01	1.41	0.04	0.002	0.11	1.06
632223	Drill Core	0.66	<0.001	0.002	<0.02	0.10	<2	0.002	<0.001	0.07	1.15	<0.02	0.02	<0.001	<0.01	<0.01	30.20	0.01	<0.001	0.14	0.16
632224	Drill Core	2.37	0.008	0.004	0.04	0.45	<2	0.013	<0.001	<0.01	1.61	<0.02	<0.01	0.001	<0.01	<0.01	1.15	0.04	0.003	0.13	1.77
632225	Drill Core	1.16	0.004	0.014	1.49	14.41	2	0.009	<0.001	0.04	6.98	<0.02	<0.01	0.041	<0.01	<0.01	5.91	0.05	0.001	0.07	0.71
632226	Drill Core	1.91	<0.001	0.001	0.06	0.53	<2	0.001	<0.001	0.07	0.62	<0.02	0.01	0.002	<0.01	<0.01	27.65	0.04	<0.001	0.12	0.24
632227	Drill Core	1.88	<0.001	<0.001	0.20	0.17	<2	<0.001	<0.001	0.09	0.46	<0.02	0.02	<0.001	<0.01	<0.01	34.12	0.04	<0.001	0.15	0.13
632228	Drill Core	1.60	0.001	0.003	0.63	4.35	<2	0.006	<0.001	0.02	1.79	<0.02	<0.01	0.012	<0.01	<0.01	6.83	0.13	0.001	0.10	0.77
632229	Drill Core	1.63	0.001	0.004	1.71	5.95	<2	0.007	<0.001	0.02	2.93	<0.02	<0.01	0.017	<0.01	<0.01	2.69	0.10	0.002	0.10	0.90
632230	Rock Pulp	0.06	<0.001	0.658	5.74	6.84	68	0.001	0.001	0.09	4.83	<0.02	0.02	0.018	0.01	<0.01	1.34	0.02	0.002	0.25	4.80



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**

Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: December 27, 2010

Page: 2 of 4 **Part** 2

CERTIFICATE OF ANALYSIS

WHI10000678.1

	Method Analyte Unit MDL	7TD	7TD	7TD	7TD	G8SG	7TD.1
		Na	K	W	S	SG	Pb
		%	%	%	%		%
		0.01	0.01	0.01	0.05	0	0.02
632201	Drill Core	0.03	0.58	<0.01	7.24	2.63	
632202	Drill Core	<0.01	1.03	<0.01	1.58	2.23	
632203	Drill Core	<0.01	0.55	<0.01	10.99	2.56	
632204	Drill Core	<0.01	1.03	<0.01	16.10	2.62	
632205	Drill Core	<0.01	0.61	<0.01	11.87	2.54	
632206	Drill Core	<0.01	0.47	<0.01	21.65	2.87	
632207	Drill Core	<0.01	0.64	<0.01	21.74	2.72	
632208	Drill Core	<0.01	0.55	<0.01	6.05	2.43	
632209	Drill Core	<0.01	0.47	<0.01	8.26	2.43	
632210	Drill Core	<0.01	0.84	<0.01	11.59	2.42	
632211	Drill Core	<0.01	0.87	<0.01	12.09	2.43	
632212	Drill Core	<0.01	0.44	<0.01	9.16	2.52	
632213	Drill Core	<0.01	0.03	<0.01	0.69	2.48	
632214	Drill Core	<0.01	0.34	<0.01	6.63	2.46	
632215	Drill Core	<0.01	0.24	<0.01	1.55	2.43	
632216	Drill Core	<0.01	0.22	<0.01	1.81	2.41	
632217	Drill Core	<0.01	0.10	<0.01	1.03	2.42	
632218	Drill Core	<0.01	0.09	<0.01	1.16	2.44	
632219	Drill Core	<0.01	0.18	<0.01	1.53	2.45	
632220	Rock	0.02	0.02	<0.01	0.11	2.58	
632221	Drill Core	<0.01	0.36	<0.01	1.44	2.33	
632222	Drill Core	<0.01	0.65	<0.01	3.10	2.26	
632223	Drill Core	<0.01	0.08	<0.01	1.69	2.53	
632224	Drill Core	<0.01	1.25	<0.01	1.99	2.19	
632225	Drill Core	<0.01	0.45	<0.01	15.41	2.80	
632226	Drill Core	<0.01	0.12	<0.01	1.18	2.51	
632227	Drill Core	<0.01	0.07	<0.01	0.91	2.53	
632228	Drill Core	<0.01	0.43	<0.01	4.23	2.48	
632229	Drill Core	<0.01	0.53	<0.01	6.41	2.46	
632230	Rock Pulp	2.26	1.39	<0.01	5.07	N.A.	



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: December 27, 2010

Page: 3 of 4 Part 1

CERTIFICATE OF ANALYSIS

WHI10000678.1

	Method Analyte Unit MDL	WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD
		Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg	Al
		kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%	%
		0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01	0.01
632231	Drill Core	1.38	0.001	0.005	1.04	6.88	<2	0.007	<0.001	0.02	6.26	<0.02	<0.01	0.017	<0.01	<0.01	1.54	0.09	0.002	0.11	1.05
632232	Drill Core	1.42	<0.001	0.002	0.66	3.57	<2	0.002	<0.001	0.07	1.00	<0.02	0.02	0.010	<0.01	<0.01	29.61	0.04	<0.001	0.10	0.24
632233	Drill Core	1.22	0.001	0.002	1.01	3.84	<2	0.002	<0.001	0.05	2.14	<0.02	0.01	0.011	<0.01	<0.01	26.09	0.04	<0.001	0.08	0.33
632234	Drill Core	1.52	<0.001	0.001	0.40	1.87	<2	0.002	<0.001	0.04	3.42	<0.02	0.02	0.005	<0.01	<0.01	28.47	0.04	<0.001	0.09	0.33
632235	Drill Core	1.88	0.003	0.004	1.02	9.16	2	0.005	<0.001	0.05	4.83	<0.02	0.01	0.024	<0.01	<0.01	18.18	0.04	0.001	0.11	0.59
632236	Drill Core	2.65	0.002	0.004	0.75	4.19	<2	0.007	<0.001	0.02	2.60	<0.02	<0.01	0.011	<0.01	<0.01	5.74	0.07	0.002	0.11	0.86
632237	Drill Core	4.79	0.003	0.006	1.78	8.14	2	0.009	<0.001	0.02	3.58	<0.02	<0.01	0.022	<0.01	<0.01	2.73	0.08	0.002	0.12	1.06
632238	Drill Core	1.19	0.002	0.004	2.11	8.22	<2	0.005	<0.001	0.02	1.58	<0.02	<0.01	0.024	<0.01	<0.01	10.75	0.13	0.002	0.12	0.78
632239	Drill Core	3.13	0.001	0.001	0.32	0.16	<2	0.003	<0.001	0.03	0.63	<0.02	0.01	<0.001	<0.01	<0.01	24.02	0.05	<0.001	0.10	0.54
632240	Drill Core	1.55	<0.001	0.003	1.25	2.24	<2	0.002	<0.001	0.04	1.21	<0.02	0.01	0.011	<0.01	<0.01	24.63	0.03	<0.001	0.09	0.34
632241	Drill Core	1.45	<0.001	0.003	1.29	2.29	<2	0.002	<0.001	0.04	1.20	<0.02	0.01	0.011	<0.01	<0.01	24.79	0.03	<0.001	0.09	0.35
632242	Drill Core	1.59	0.002	0.002	0.03	0.17	<2	0.006	<0.001	0.03	0.79	<0.02	0.01	<0.001	<0.01	<0.01	21.77	0.06	0.001	0.13	0.91
632243	Drill Core	0.99	0.003	0.004	0.78	1.69	<2	0.007	<0.001	0.02	0.90	<0.02	<0.01	0.004	<0.01	<0.01	10.36	0.08	0.002	0.14	1.16
632244	Drill Core	0.68	0.003	0.014	4.55	17.82	5	0.011	<0.001	0.02	4.23	<0.02	<0.01	0.043	<0.01	<0.01	2.93	0.07	0.002	0.10	0.86
632245	Drill Core	1.29	0.002	0.002	0.09	0.22	<2	0.007	<0.001	<0.01	0.88	<0.02	<0.01	<0.001	<0.01	<0.01	2.07	0.07	0.002	0.09	0.80
632246	Drill Core	0.92	<0.001	0.001	0.33	0.93	<2	0.002	<0.001	0.02	0.37	<0.02	<0.01	0.004	<0.01	<0.01	15.67	0.03	<0.001	0.05	0.25
632247	Drill Core	1.05	<0.001	0.004	9.39	13.09	3	<0.001	<0.001	0.02	0.91	<0.02	<0.01	0.061	<0.01	<0.01	9.88	0.03	0.002	0.03	0.12
632248	Drill Core	0.82	0.001	0.002	0.12	0.18	<2	0.005	<0.001	0.02	1.01	<0.02	<0.01	<0.001	<0.01	<0.01	13.23	0.03	<0.001	0.07	0.44
632249	Drill Core	2.76	0.004	0.012	0.43	0.74	<2	0.014	<0.001	0.02	3.17	<0.02	<0.01	0.003	<0.01	<0.01	6.36	0.23	0.003	0.16	1.25
632250	Rock	0.46	<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	0.02	0.13	<0.02	0.01	<0.001	<0.01	<0.01	21.14	0.03	<0.001	11.09	0.13
632251	Drill Core	1.56	0.002	0.003	0.06	0.88	<2	0.005	<0.001	0.03	1.92	<0.02	<0.01	0.003	<0.01	<0.01	8.90	0.13	<0.001	0.06	0.33
632252	Drill Core	2.03	0.002	0.007	0.05	0.28	<2	0.006	<0.001	0.04	1.34	<0.02	0.01	0.001	<0.01	<0.01	21.70	0.12	0.001	0.09	0.42
632253	Drill Core	1.22	0.005	0.016	0.24	1.24	3	0.011	<0.001	0.02	1.05	<0.02	<0.01	0.005	<0.01	<0.01	10.50	0.76	0.003	0.12	0.82
632254	Drill Core	2.33	0.004	0.014	0.07	0.69	<2	0.007	<0.001	0.03	1.09	<0.02	0.01	0.003	<0.01	<0.01	18.76	0.66	0.003	0.13	0.39
632255	Drill Core	2.03	0.005	0.014	0.22	0.57	<2	0.009	<0.001	0.02	2.46	<0.02	0.01	0.003	<0.01	<0.01	19.16	0.21	0.003	0.13	0.80
632256	Drill Core	2.57	0.003	0.007	0.07	0.65	<2	0.007	<0.001	0.02	0.65	<0.02	<0.01	0.003	<0.01	<0.01	14.88	0.25	0.002	0.08	0.48
632257	Drill Core	0.35	0.002	0.007	0.07	0.43	<2	0.007	<0.001	0.02	0.38	<0.02	0.01	0.002	<0.01	<0.01	17.80	0.21	0.003	0.08	0.51
632258	Drill Core	2.20	0.008	0.014	0.16	4.35	4	0.017	<0.001	<0.01	1.64	<0.02	<0.01	0.016	<0.01	<0.01	2.78	0.37	0.005	0.18	1.38
632259	Drill Core	2.10	0.003	0.013	0.05	0.28	<2	0.008	<0.001	0.02	0.60	<0.02	0.01	0.001	<0.01	<0.01	18.99	0.29	0.004	0.09	0.64
632260	Rock Pulp	0.06	<0.001	0.480	1.42	2.93	17	<0.001	<0.001	0.44	2.60	<0.02	0.02	0.018	<0.01	<0.01	4.70	0.01	0.001	0.32	4.29



Acme Analytical Laboratories (Vancouver) Ltd.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client:

Selwyn Resources Ltd.

Suite 700 - 509 Richards Street

Vancouver BC V6B 2Z6 Canada

Project:

Selwyn Project

Report Date:

December 27, 2010

Page:

3 of 4

Part 2

CERTIFICATE OF ANALYSIS

WHI10000678.1

	Method Analyte Unit MDL	7TD	7TD	7TD	7TD	G8SG	7TD.1
		Na	K	W	S	SG	Pb
		%	%	%	%		%
		0.01	0.01	0.01	0.05	0	0.02
632231	Drill Core	<0.01	0.66	<0.01	10.58	2.58	
632232	Drill Core	<0.01	0.12	<0.01	3.29	2.57	
632233	Drill Core	<0.01	0.17	<0.01	4.79	2.60	
632234	Drill Core	<0.01	0.17	<0.01	5.20	2.57	
632235	Drill Core	<0.01	0.31	<0.01	9.79	2.74	
632236	Drill Core	<0.01	0.50	<0.01	5.10	2.43	
632237	Drill Core	<0.01	0.62	<0.01	8.11	2.49	
632238	Drill Core	<0.01	0.43	<0.01	6.19	2.56	
632239	Drill Core	<0.01	0.28	<0.01	1.00	2.45	
632240	Drill Core	<0.01	0.17	<0.01	2.85	2.57	
632241	Drill Core	<0.01	0.18	<0.01	2.88	2.59	
632242	Drill Core	<0.01	0.49	<0.01	1.06	2.40	
632243	Drill Core	<0.01	0.71	<0.01	1.94	2.39	
632244	Drill Core	<0.01	0.51	<0.01	13.74	2.74	
632245	Drill Core	<0.01	0.50	<0.01	0.93	2.33	
632246	Drill Core	<0.01	0.13	<0.01	0.93	2.48	
632247	Drill Core	<0.01	0.07	<0.01	8.89	2.97	
632248	Drill Core	<0.01	0.25	<0.01	1.22	2.45	
632249	Drill Core	<0.01	0.75	<0.01	3.99	2.30	
632250	Rock	0.01	0.03	<0.01	0.17	2.61	
632251	Drill Core	<0.01	0.18	<0.01	2.51	2.54	
632252	Drill Core	<0.01	0.22	<0.01	1.77	2.49	
632253	Drill Core	<0.01	0.44	<0.01	1.78	2.32	
632254	Drill Core	<0.01	0.21	<0.01	1.65	2.42	
632255	Drill Core	<0.01	0.45	<0.01	3.23	2.41	
632256	Drill Core	<0.01	0.26	<0.01	1.06	2.38	
632257	Drill Core	0.02	0.27	<0.01	0.63	2.38	
632258	Drill Core	0.06	0.77	<0.01	3.93	2.21	
632259	Drill Core	0.02	0.34	<0.01	0.79	2.35	
632260	Rock Pulp	1.69	1.28	<0.01	3.26	N.A.	



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: Selwyn Resources Ltd.
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: December 27, 2010

Page: 4 of 4 **Part** 1

CERTIFICATE OF ANALYSIS

WHI10000678.1

	Method Analyte Unit MDL	WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD
		Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg	Al
		kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%	%
		0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01	0.01
632261	Drill Core	2.83	0.008	0.020	0.35	1.41	<2	0.017	<0.001	0.01	1.96	<0.02	<0.01	0.005	<0.01	<0.01	5.32	0.37	0.008	0.15	1.34
632262	Drill Core	3.15	0.006	0.020	0.56	2.61	5	0.014	<0.001	0.01	5.91	<0.02	<0.01	0.010	<0.01	<0.01	7.44	0.28	0.007	0.13	1.11
632263	Drill Core	2.56	0.007	0.017	0.09	1.02	<2	0.014	<0.001	0.01	0.67	<0.02	<0.01	0.004	<0.01	<0.01	8.17	0.22	0.006	0.14	1.20
632264	Drill Core	1.98	0.010	0.010	0.05	0.53	3	0.016	<0.001	<0.01	2.03	<0.02	<0.01	0.002	<0.01	<0.01	4.83	0.19	0.005	0.16	1.33
632265	Drill Core	1.93	0.008	0.007	0.08	0.87	<2	0.012	<0.001	0.01	1.94	<0.02	<0.01	0.004	<0.01	<0.01	9.85	0.77	0.005	0.14	1.01
632266	Drill Core	0.64	0.003	0.003	0.31	1.75	<2	0.011	<0.001	0.02	1.05	<0.02	<0.01	0.009	<0.01	<0.01	7.52	0.19	0.003	0.16	1.37
632267	Drill Core	0.67	<0.001	0.004	>10	17.79	11	0.003	<0.001	0.03	3.06	<0.02	<0.01	0.095	0.01	<0.01	6.62	0.04	<0.001	0.04	0.23
632268	Drill Core	1.77	0.003	0.002	0.39	1.86	<2	0.010	<0.001	0.03	0.84	<0.02	<0.01	0.009	<0.01	<0.01	10.80	0.14	0.003	0.16	1.35
632269	Drill Core	1.22	0.003	0.003	0.11	0.75	<2	0.008	<0.001	0.01	2.81	<0.02	<0.01	0.003	<0.01	<0.01	3.54	0.18	0.002	0.08	0.66
632270	Drill Core	0.24	<0.001	0.003	0.04	0.09	<2	0.003	<0.001	0.06	0.47	<0.02	0.01	<0.001	<0.01	<0.01	20.49	0.08	0.001	0.06	0.19
632271	Drill Core	0.29	<0.001	0.003	0.03	0.12	<2	0.003	<0.001	0.05	0.36	<0.02	0.01	<0.001	<0.01	<0.01	19.69	0.08	0.002	0.06	0.20
632272	Drill Core	2.81	0.006	0.012	0.18	1.60	<2	0.013	<0.001	0.02	2.12	<0.02	<0.01	0.009	<0.01	<0.01	9.89	0.35	0.006	0.14	1.07
632273	Drill Core	1.28	0.009	0.031	0.14	1.38	3	0.014	<0.001	0.02	0.83	<0.02	0.01	0.007	<0.01	<0.01	11.87	1.62	0.007	0.13	0.98
632274	Drill Core	2.42	0.004	0.013	0.09	0.96	<2	0.009	<0.001	0.02	1.48	<0.02	<0.01	0.004	<0.01	<0.01	11.06	0.24	0.004	0.11	0.76
632275	Drill Core	2.66	0.002	0.007	<0.02	<0.01	<2	0.013	<0.001	0.01	2.27	<0.02	<0.01	<0.001	<0.01	<0.01	4.81	0.07	0.010	0.37	3.92
632276	Drill Core	1.32	0.003	0.007	<0.02	0.03	<2	0.014	<0.001	<0.01	2.10	<0.02	<0.01	<0.001	<0.01	<0.01	1.35	0.10	0.012	0.39	4.48



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**

Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: December 27, 2010

Page: 4 of 4 **Part** 2

CERTIFICATE OF ANALYSIS

WHI10000678.1

	Method	7TD	7TD	7TD	7TD	G8SG	7TD.1
	Analyte	Na	K	W	S	SG	Pb
	Unit	%	%	%	%		%
	MDL	0.01	0.01	0.01	0.05	0	0.02
632261	Drill Core	0.02	0.78	<0.01	2.97	2.19	
632262	Drill Core	<0.01	0.66	<0.01	8.72	2.37	
632263	Drill Core	<0.01	0.71	<0.01	1.20	2.10	
632264	Drill Core	<0.01	0.75	<0.01	2.50	2.17	
632265	Drill Core	<0.01	0.58	<0.01	2.61	2.23	
632266	Drill Core	<0.01	0.87	<0.01	1.99	2.17	
632267	Drill Core	<0.01	0.14	<0.01	14.26	3.07	13.39
632268	Drill Core	<0.01	0.87	<0.01	1.84	2.21	
632269	Drill Core	<0.01	0.37	<0.01	3.56	2.32	
632270	Drill Core	<0.01	0.10	<0.01	0.49	2.45	
632271	Drill Core	<0.01	0.11	<0.01	0.38	2.41	
632272	Drill Core	<0.01	0.62	<0.01	3.27	2.20	
632273	Drill Core	<0.01	0.56	<0.01	1.58	2.12	
632274	Drill Core	<0.01	0.42	<0.01	2.13	2.25	
632275	Drill Core	0.01	1.53	<0.01	2.54	2.18	
632276	Drill Core	0.01	1.88	<0.01	2.28	2.17	



Acme Analytical Laboratories (Vancouver) Ltd.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: **Selwyn Resources Ltd.**

Suite 700 - 509 Richards Street

Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: December 27, 2010

Page: 1 of 2 Part 1

QUALITY CONTROL REPORT

WHI10000678.1

	Method Analyte Unit MDL	WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	
		Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg	Al
		kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%	%
		0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01	0.01
Pulp Duplicates																					
632246	Drill Core	0.92	<0.001	0.001	0.33	0.93	<2	0.002	<0.001	0.02	0.37	<0.02	<0.01	0.004	<0.01	<0.01	15.67	0.03	<0.001	0.05	0.25
REP 632246	QC		<0.001	0.001	0.33	0.92	<2	0.002	<0.001	0.02	0.37	<0.02	<0.01	0.004	<0.01	<0.01	15.58	0.03	<0.001	0.05	0.25
632266	Drill Core	0.64	0.003	0.003	0.31	1.75	<2	0.011	<0.001	0.02	1.05	<0.02	<0.01	0.009	<0.01	<0.01	7.52	0.19	0.003	0.16	1.37
REP 632266	QC		0.003	0.003	0.31	1.79	<2	0.011	<0.001	0.02	1.06	<0.02	<0.01	0.009	<0.01	<0.01	7.48	0.19	0.004	0.16	1.37
632267	Drill Core	0.67	<0.001	0.004	>10	17.79	11	0.003	<0.001	0.03	3.06	<0.02	<0.01	0.095	0.01	<0.01	6.62	0.04	<0.001	0.04	0.23
REP 632267	QC																				
Core Reject Duplicates																					
632208	Drill Core	0.97	0.004	0.004	0.45	1.99	<2	0.009	<0.001	0.01	4.50	<0.02	<0.01	0.006	<0.01	<0.01	0.75	0.03	0.002	0.09	0.92
DUP 632208	QC		0.004	0.004	0.44	1.96	<2	0.009	<0.001	0.01	4.43	<0.02	<0.01	0.006	<0.01	<0.01	0.76	0.03	0.002	0.08	0.91
632243	Drill Core	0.99	0.003	0.004	0.78	1.69	<2	0.007	<0.001	0.02	0.90	<0.02	<0.01	0.004	<0.01	<0.01	10.36	0.08	0.002	0.14	1.16
DUP 632243	QC		0.003	0.004	0.81	1.69	<2	0.008	<0.001	0.02	0.91	<0.02	<0.01	0.004	<0.01	<0.01	10.22	0.07	0.002	0.14	1.15
Reference Materials																					
STD CCU-1C	Standard																				
STD CZN-3	Standard																				
STD OREAS131A	Standard		<0.001	0.032	1.76	2.93	31	0.003	0.002	0.18	5.92	<0.02	<0.01	0.008	<0.01	<0.01	5.46	0.06	0.002	3.13	4.61
STD OREAS131A	Standard		<0.001	0.033	1.67	2.89	31	0.003	0.002	0.17	5.90	<0.02	<0.01	0.008	<0.01	<0.01	5.41	0.05	0.002	3.12	4.57
STD OREAS131A	Standard		<0.001	0.033	1.77	2.92	32	0.003	0.002	0.18	5.84	<0.02	<0.01	0.008	<0.01	<0.01	5.43	0.05	0.002	3.24	4.75
STD OREAS131A	Standard		<0.001	0.032	1.72	2.90	31	0.003	0.002	0.17	5.95	<0.02	<0.01	0.008	<0.01	<0.01	5.46	0.06	0.003	3.13	4.58
STD PTC-1A	Standard																				
STD R4T	Standard		0.064	0.516	1.61	3.50	89	0.357	0.042	0.09	24.79	<0.02	0.02	0.019	0.01	<0.01	2.21	0.05	0.018	1.44	3.91
STD R4T	Standard		0.063	0.515	1.50	3.46	88	0.351	0.041	0.09	24.37	<0.02	0.02	0.019	0.02	<0.01	2.20	0.04	0.019	1.41	3.91
STD R4T	Standard		0.064	0.520	1.60	3.45	91	0.358	0.041	0.09	24.45	<0.02	0.02	0.019	0.02	<0.01	2.22	0.04	0.018	1.46	4.04
STD R4T	Standard		0.065	0.514	1.57	3.46	89	0.355	0.041	0.09	24.68	<0.02	0.02	0.019	0.02	<0.01	2.18	0.05	0.019	1.44	3.93
STD SARM 71	Standard																				
STD SU-1B	Standard		<0.001	1.164	<0.02	0.03	7	1.932	0.066	0.07	25.29	<0.02	0.03	<0.001	<0.01	<0.01	2.19	0.07	0.031	1.75	4.28
STD SU-1B	Standard		<0.001	1.182	<0.02	0.03	6	1.945	0.067	0.07	25.29	<0.02	0.03	<0.001	<0.01	<0.01	2.22	0.06	0.031	1.76	4.32
STD SU-1B	Standard		<0.001	1.218	<0.02	0.02	5	2.006	0.067	0.07	25.53	<0.02	0.03	<0.001	<0.01	<0.01	2.25	0.06	0.030	1.83	4.45
STD SU-1B	Standard		<0.001	1.209	<0.02	0.03	7	1.994	0.069	0.07	25.93	<0.02	0.03	<0.001	<0.01	<0.01	2.24	0.08	0.033	1.83	4.38



Acme Analytical Laboratories (Vancouver) Ltd.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: **Selwyn Resources Ltd.**

Suite 700 - 509 Richards Street

Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: December 27, 2010

Page: 1 of 2 **Part** 2

QUALITY CONTROL REPORT

WHI10000678.1

Method		7TD	7TD	7TD	7TD	G8SG	7TD.1
Analyte		Na	K	W	S	SG	Pb
Unit		%	%	%	%		%
MDL		0.01	0.01	0.01	0.05	0	0.02
Pulp Duplicates							
632246	Drill Core	<0.01	0.13	<0.01	0.93	2.48	
REP 632246	QC	<0.01	0.13	<0.01	0.92		
632266	Drill Core	<0.01	0.87	<0.01	1.99	2.17	
REP 632266	QC	<0.01	0.86	<0.01	1.97		
632267	Drill Core	<0.01	0.14	<0.01	14.26	3.07	13.39
REP 632267	QC						13.35
Core Reject Duplicates							
632208	Drill Core	<0.01	0.55	<0.01	6.05	2.43	
DUP 632208	QC	<0.01	0.54	<0.01	5.99	2.42	
632243	Drill Core	<0.01	0.71	<0.01	1.94	2.39	
DUP 632243	QC	<0.01	0.71	<0.01	1.93	2.33	
Reference Materials							
STD CCU-1C	Standard						0.39
STD CZN-3	Standard						0.10
STD OREAS131A	Standard	0.15	3.48	<0.01	4.99		
STD OREAS131A	Standard	0.16	3.05	<0.01	4.93		
STD OREAS131A	Standard	0.16	3.39	<0.01	5.03		
STD OREAS131A	Standard	0.15	3.45	<0.01	4.88		
STD PTC-1A	Standard						0.04
STD R4T	Standard	0.95	1.21	<0.01	13.93		
STD R4T	Standard	0.94	1.19	<0.01	12.57		
STD R4T	Standard	0.93	1.20	<0.01	12.78		
STD R4T	Standard	0.94	1.22	<0.01	11.77		
STD SARM 71	Standard						<0.02
STD SU-1B	Standard	1.69	0.63	<0.01	9.65		
STD SU-1B	Standard	1.70	0.63	<0.01	8.33		
STD SU-1B	Standard	1.71	0.62	<0.01	10.72		
STD SU-1B	Standard	1.75	0.64	<0.01	8.41		



Acme Analytical Laboratories (Vancouver) Ltd.
1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: December 27, 2010

Page: 2 of 2 Part 1

QUALITY CONTROL REPORT

WHI10000678.1

		WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD
		Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg	Al
		kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%	%
		0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01	0.01
STD CZN-3 Expected																					
STD CCU-1C Expected																					
STD PTC-1A Expected																					
STD R4T Expected			0.062	0.502	1.518	3.376	86	0.339	0.039	0.086	24.07	0.0087	0.0185	0.018	0.0138	0.0018	2.166	0.045	0.018	1.384	3.897
STD OREAS131A Expected			0.001	0.0322	1.72	2.83	30.9	0.0027	0.0023	0.1722	5.8166	0.0082	0.0028	0.0081	0.0047	0.001	5.286	0.0536	0.0025	3.1182	4.6057
STD SU-1B Expected			0.0004	1.185	0.0058	0.0235	6.4	1.97	0.0672	0.0703	25.54	0.00025	0.03	0.0003	0.00002	0.0003	2.21	0.06	0.032	1.79	4.39
BLK	Blank	<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	<0.01	<0.01	<0.02	<0.01	<0.001	<0.01	<0.01	<0.01	<0.01	<0.01	<0.001	<0.01	<0.01
BLK	Blank	<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	<0.01	<0.01	<0.02	<0.01	<0.001	<0.01	<0.01	<0.01	<0.01	<0.01	<0.001	<0.01	<0.01
BLK	Blank	<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	<0.01	<0.01	<0.02	<0.01	<0.001	<0.01	<0.01	<0.01	<0.01	<0.01	<0.001	<0.01	<0.01
BLK	Blank																				
BLK	Blank	<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	<0.01	<0.01	<0.02	<0.01	<0.001	<0.01	<0.01	<0.01	<0.01	<0.01	<0.001	<0.01	<0.01
Prep Wash																					
G1	Prep Blank	<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	0.07	2.38	<0.02	0.08	<0.001	<0.01	<0.01	2.39	0.08	0.001	0.63	7.52	
G1	Prep Blank	<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	0.08	2.44	<0.02	0.08	<0.001	<0.01	<0.01	2.40	0.08	0.001	0.63	7.56	



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: December 27, 2010

Page: 2 of 2 **Part** 2

QUALITY CONTROL REPORT

WHI10000678.1

		7TD Na %	7TD K %	7TD W %	7TD S %	G8SG SG 0	7TD.1 Pb %
		0.01	0.01	0.01	0.05	0	0.02
STD CZN-3 Expected							0.113
STD CCU-1C Expected							0.34
STD PTC-1A Expected							0.05
STD R4T Expected		0.9	1.153	0.00016	12.9903		
STD OREAS131A Expected		0.1501	3.1584	0.0005	4.8		
STD SU-1B Expected		1.662	0.6	0.0007	8.76		
BLK	Blank	<0.01	<0.01	<0.01	<0.05		
BLK	Blank	<0.01	<0.01	<0.01	<0.05		
BLK	Blank	<0.01	<0.01	<0.01	<0.05		
BLK	Blank						<0.02
BLK	Blank	<0.01	<0.01	<0.01	<0.05		
Prep Wash							
G1	Prep Blank	2.72	3.03	<0.01	<0.05	2.61	
G1	Prep Blank	2.74	3.02	<0.01	<0.05	2.61	



1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: Selwyn Resources Ltd.

Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Submitted By: Jason K. Dunning

Receiving Lab: Canada-Whitehorse

Received: December 06, 2010

Report Date: December 22, 2010

Page: 1 of 3

CERTIFICATE OF ANALYSIS

WHI10000677.1

CLIENT JOB INFORMATION

Project: Selwyn Project
Shipment ID:
P.O. Number: 1124
Number of Samples: 50

SAMPLE DISPOSAL

STOR-PLP Store After 90 days Invoice for Storage
STOR-RJT Store After 90 days Invoice for Storage

Acme does not accept responsibility for samples left at the laboratory after 90 days without prior written instructions for sample storage or return.

Invoice To: Selwyn Resources Ltd.
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6
Canada

CC:

SAMPLE PREPARATION AND ANALYTICAL PROCEDURES

Method Code	Number of Samples	Code Description	Test Wgt (g)	Report Status	Lab
R200-250	48	Crush split and pulverize 250g drill core to 200 mesh			WHI
7TD2	50	4 Acid digestion ICP-ES analysis.	0.5	Completed	VAN
G812	50	Specific Gravity on Pulp		Completed	VAN
7TD.1	5	4 Acid digestion ICP-ES analysis	0.1	Completed	VAN

ADDITIONAL COMMENTS



This report supersedes all previous preliminary and final reports with this file number dated prior to the date on this certificate. Signature indicates final approval; preliminary reports are unsigned and should be used for reference only.

All results are considered the confidential property of the client. Acme assumes the liabilities for actual cost of analysis only.

“**” asterisk indicates that an analytical result could not be provided due to unusually high levels of interference from other elements.



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: December 22, 2010

Page: 2 of 3 Part 1

CERTIFICATE OF ANALYSIS

WHI10000677.1

	Method Analyte Unit MDL	WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD
		Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg
		kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%
		0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01
632801	Drill Core	1.12	0.004	0.002	0.22	0.34	<2	0.008	<0.001	0.02	1.16	<0.02	<0.01	0.001	<0.01	<0.01	6.53	0.04	0.002	0.14
632802	Drill Core	1.09	0.003	0.011	1.85	8.96	4	0.009	<0.001	0.01	5.40	<0.02	<0.01	0.030	<0.01	<0.01	0.37	0.05	0.002	0.09
632803	Drill Core	0.77	<0.001	0.015	0.29	0.06	<2	0.002	<0.001	0.01	30.31	<0.02	<0.01	<0.001	<0.01	<0.01	7.81	0.01	<0.001	0.02
632804	Drill Core	0.59	<0.001	0.002	0.53	1.89	<2	0.002	<0.001	0.09	0.89	<0.02	0.01	0.007	<0.01	<0.01	27.35	0.04	<0.001	0.15
632805	Drill Core	1.34	0.002	0.007	1.35	3.16	<2	0.005	<0.001	0.02	5.35	<0.02	<0.01	0.009	<0.01	<0.01	7.43	0.05	<0.001	0.07
632806	Drill Core	3.25	<0.001	<0.001	0.30	0.39	<2	0.002	<0.001	0.05	0.40	<0.02	0.01	0.001	<0.01	<0.01	28.67	0.04	<0.001	0.09
632807	Drill Core	0.66	<0.001	0.001	0.13	1.16	<2	0.004	<0.001	0.01	0.66	<0.02	<0.01	0.004	<0.01	<0.01	5.38	0.09	<0.001	0.08
632808	Drill Core	3.73	<0.001	<0.001	0.14	0.32	<2	0.001	<0.001	0.05	0.76	<0.02	0.02	0.001	<0.01	<0.01	28.83	0.04	<0.001	0.10
632809	Drill Core	2.95	0.004	0.015	1.49	10.89	3	0.008	<0.001	0.04	8.55	<0.02	<0.01	0.030	<0.01	<0.01	6.43	0.06	0.001	0.07
632810	Drill Core	1.18	<0.001	0.001	0.27	1.04	<2	0.001	<0.001	0.05	1.92	<0.02	0.01	0.003	<0.01	<0.01	28.65	0.02	<0.001	0.08
632811	Drill Core	1.35	<0.001	0.001	0.60	1.42	<2	0.001	<0.001	0.05	1.84	<0.02	0.01	0.004	<0.01	<0.01	27.02	0.02	<0.001	0.08
632812	Drill Core	2.37	<0.001	0.002	0.91	3.20	<2	0.002	<0.001	0.05	1.18	<0.02	0.01	0.009	<0.01	<0.01	26.82	0.06	<0.001	0.07
632813	Drill Core	1.33	<0.001	0.002	1.18	2.46	<2	0.002	<0.001	0.04	1.15	<0.02	0.02	0.009	<0.01	<0.01	28.53	0.04	<0.001	0.11
632814	Drill Core	1.99	0.002	0.003	1.22	3.65	<2	0.005	<0.001	0.02	2.50	<0.02	<0.01	0.010	<0.01	<0.01	8.97	0.05	0.001	0.10
632815	Drill Core	1.76	0.002	0.005	1.55	7.84	<2	0.005	<0.001	0.01	2.16	<0.02	<0.01	0.023	<0.01	<0.01	2.83	0.05	0.001	0.07
632816	Drill Core	2.41	0.001	0.003	1.36	4.82	<2	0.004	<0.001	0.01	1.38	<0.02	<0.01	0.013	<0.01	<0.01	7.91	0.05	0.001	0.07
632817	Drill Core	3.02	<0.001	0.001	0.83	0.21	<2	0.003	<0.001	0.04	0.69	<0.02	0.02	<0.001	<0.01	<0.01	27.78	0.04	0.001	0.11
632818	Drill Core	1.83	0.002	0.004	0.97	3.63	2	0.007	<0.001	0.02	1.58	<0.02	<0.01	0.011	<0.01	<0.01	10.40	0.06	0.002	0.11
632819	Drill Core	2.70	<0.001	0.004	>10	18.29	11	0.001	<0.001	0.01	1.76	<0.02	<0.01	0.108	<0.01	<0.01	8.56	0.06	<0.001	0.02
632820	Rock	0.42	<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	0.02	0.16	<0.02	<0.01	<0.001	<0.01	<0.01	20.90	0.03	<0.001	11.04
632821	Drill Core	2.67	<0.001	0.005	>10	23.18	12	<0.001	<0.001	0.01	0.67	<0.02	<0.01	0.123	<0.01	<0.01	5.73	0.09	<0.001	0.03
632822	Drill Core	1.54	<0.001	0.005	>10	25.04	13	<0.001	<0.001	<0.01	0.74	<0.02	<0.01	0.130	<0.01	<0.01	1.55	0.10	<0.001	<0.01
632823	Drill Core	2.30	<0.001	0.004	>10	10.08	13	0.003	<0.001	0.01	2.55	<0.02	<0.01	0.063	<0.01	<0.01	6.06	0.05	<0.001	0.04
632824	Drill Core	2.48	0.001	0.005	>10	13.99	16	0.002	<0.001	<0.01	1.77	<0.02	<0.01	0.088	<0.01	<0.01	0.88	0.06	<0.001	0.03
632825	Drill Core	2.36	<0.001	0.004	9.90	9.72	9	0.002	<0.001	<0.01	2.14	<0.02	<0.01	0.049	<0.01	<0.01	0.65	0.05	<0.001	0.04
632826	Drill Core	2.18	0.001	0.003	0.10	0.14	<2	0.003	<0.001	0.04	1.02	<0.02	0.02	<0.001	<0.01	<0.01	29.16	0.02	0.001	0.09
632827	Drill Core	1.78	<0.001	0.002	0.50	0.03	<2	0.003	<0.001	0.04	0.51	<0.02	0.02	<0.001	<0.01	<0.01	29.22	0.11	<0.001	0.10
632828	Drill Core	1.29	0.002	0.004	0.13	0.71	<2	0.008	<0.001	0.03	1.65	<0.02	<0.01	0.002	<0.01	<0.01	9.86	0.48	0.002	0.08
632829	Drill Core	3.05	0.004	0.009	0.08	1.79	3	0.010	<0.001	0.02	2.12	<0.02	<0.01	0.008	<0.01	<0.01	7.57	0.62	0.003	0.10
632830	Rock Pulp	0.06	<0.001	0.654	5.74	6.51	67	<0.001	<0.001	0.09	4.77	<0.02	0.02	0.018	<0.01	<0.01	1.32	0.02	0.001	0.24



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: December 22, 2010

Page: 2 of 3 **Part** 2

CERTIFICATE OF ANALYSIS

WHI10000677.1

	Method Analyte Unit MDL	7TD	7TD	7TD	7TD	G8SG	7TD.1
		Na	K	W	S	SG	Pb
		%	%	%	%		%
		0.01	0.01	0.01	0.05	0	0.02
632801	Drill Core	0.10	0.82	<0.01	1.40	2.34	
632802	Drill Core	<0.01	0.53	<0.01	10.71	2.57	
632803	Drill Core	<0.01	0.28	<0.01	35.09	3.62	
632804	Drill Core	<0.01	0.14	<0.01	2.03	2.51	
632805	Drill Core	<0.01	0.32	<0.01	7.83	2.56	
632806	Drill Core	<0.01	0.11	<0.01	0.67	2.51	
632807	Drill Core	<0.01	0.31	<0.01	1.21	2.40	
632808	Drill Core	0.01	0.09	<0.01	1.01	2.52	
632809	Drill Core	<0.01	0.34	<0.01	15.74	2.69	
632810	Drill Core	<0.01	0.04	<0.01	2.83	2.57	
632811	Drill Core	<0.01	0.06	<0.01	2.98	2.67	
632812	Drill Core	<0.01	0.09	<0.01	3.14	2.64	
632813	Drill Core	<0.01	0.11	<0.01	2.81	2.67	
632814	Drill Core	<0.01	0.34	<0.01	4.97	2.57	
632815	Drill Core	<0.01	0.35	<0.01	6.77	2.65	
632816	Drill Core	<0.01	0.34	<0.01	4.17	2.58	
632817	Drill Core	<0.01	0.25	<0.01	1.02	2.51	
632818	Drill Core	<0.01	0.55	<0.01	3.86	2.48	
632819	Drill Core	<0.01	0.04	<0.01	13.91	3.30	18.28
632820	Rock	0.02	0.02	<0.01	<0.05	2.61	
632821	Drill Core	<0.01	0.03	<0.01	15.35	3.41	18.59
632822	Drill Core	<0.01	0.03	<0.01	16.35	3.39	18.05
632823	Drill Core	<0.01	0.11	<0.01	10.80	3.01	18.07
632824	Drill Core	<0.01	0.14	<0.01	11.77	3.15	18.52
632825	Drill Core	<0.01	0.16	<0.01	9.01	2.86	
632826	Drill Core	<0.01	0.16	<0.01	1.29	2.48	
632827	Drill Core	<0.01	0.15	<0.01	0.64	2.53	
632828	Drill Core	<0.01	0.29	<0.01	2.25	2.34	
632829	Drill Core	<0.01	0.44	<0.01	3.41	2.32	
632830	Rock Pulp	2.28	1.29	<0.01	6.19	N.A.	



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: December 22, 2010

Page: 3 of 3 Part 1

CERTIFICATE OF ANALYSIS

WHI10000677.1

	Method Analyte Unit MDL	WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	
		Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg	Al
		kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%	%
		0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01	0.01
632831	Drill Core	0.91	0.010	0.036	0.32	0.27	3	0.015	<0.001	0.02	1.30	<0.02	0.01	0.001	<0.01	<0.01	14.67	1.02	0.006	0.14	0.98
632832	Drill Core	2.04	0.001	0.007	0.07	0.11	<2	0.003	<0.001	0.03	3.92	<0.02	0.01	<0.001	<0.01	<0.01	29.05	0.17	0.001	0.08	0.13
632833	Drill Core	1.51	0.003	0.010	0.06	0.17	2	0.005	<0.001	0.03	3.67	<0.02	0.02	<0.001	<0.01	<0.01	26.65	0.24	0.002	0.08	0.33
632834	Drill Core	2.12	0.004	0.013	0.48	0.72	5	0.008	<0.001	0.02	1.31	<0.02	0.01	0.002	<0.01	<0.01	17.66	0.28	0.003	0.11	0.60
632835	Drill Core	2.17	0.002	0.005	0.02	0.14	<2	0.004	<0.001	0.02	0.33	<0.02	<0.01	<0.001	<0.01	<0.01	17.70	0.21	0.001	0.07	0.29
632836	Drill Core	2.34	0.002	0.007	0.06	0.34	<2	0.005	<0.001	0.01	2.27	<0.02	<0.01	0.001	<0.01	<0.01	10.23	0.19	0.002	0.06	0.36
632837	Drill Core	1.46	0.001	0.005	0.03	0.47	<2	0.003	<0.001	0.02	0.72	<0.02	0.01	0.001	<0.01	<0.01	20.65	0.06	0.001	0.06	0.23
632838	Drill Core	3.34	0.003	0.019	0.09	0.31	3	0.007	<0.001	0.01	3.03	<0.02	<0.01	<0.001	<0.01	<0.01	12.03	0.18	0.003	0.08	0.54
632839	Drill Core	2.58	0.006	0.019	0.21	0.11	3	0.011	<0.001	0.02	0.56	<0.02	<0.01	<0.001	<0.01	<0.01	12.76	0.31	0.004	0.11	0.85
632840	Drill Core	1.33	0.005	0.010	0.15	2.20	5	0.011	<0.001	0.02	0.88	<0.02	<0.01	0.007	<0.01	<0.01	12.15	0.19	0.004	0.10	0.78
632841	Drill Core	1.55	0.005	0.011	0.09	1.45	4	0.011	<0.001	0.02	1.15	<0.02	<0.01	0.005	<0.01	<0.01	11.96	0.19	0.004	0.10	0.78
632842	Drill Core	0.54	0.007	0.021	0.08	5.48	7	0.014	<0.001	0.01	1.21	<0.02	<0.01	0.018	<0.01	<0.01	4.38	0.09	0.003	0.11	0.91
632843	Drill Core	2.46	0.010	0.019	0.08	0.24	<2	0.018	<0.001	0.01	1.12	<0.02	<0.01	<0.001	<0.01	<0.01	5.94	0.22	0.005	0.14	1.26
632844	Drill Core	2.88	<0.001	0.002	<0.02	<0.01	<2	0.002	<0.001	0.04	1.62	<0.02	0.01	<0.001	<0.01	<0.01	24.70	0.02	0.003	0.36	2.43
632845	Drill Core	1.72	<0.001	0.001	<0.02	<0.01	<2	0.001	<0.001	0.04	1.19	<0.02	0.02	<0.001	<0.01	<0.01	29.34	0.02	0.002	0.33	1.90
632846	Drill Core	1.46	0.003	0.003	0.02	<0.01	<2	0.011	<0.001	0.03	1.95	<0.02	0.01	<0.001	<0.01	<0.01	19.67	0.42	0.005	0.28	2.35
632847	Drill Core	3.11	0.008	0.010	0.03	0.05	<2	0.028	<0.001	0.02	2.74	<0.02	<0.01	<0.001	<0.01	<0.01	5.15	0.16	0.014	0.38	3.59
632848	Drill Core	2.97	0.005	0.011	0.03	<0.01	<2	0.025	<0.001	0.01	2.81	<0.02	<0.01	<0.001	<0.01	<0.01	2.97	0.38	0.011	0.39	4.05
632849	Rock Pulp	0.06	<0.001	0.476	1.45	3.02	18	<0.001	<0.001	0.43	2.64	<0.02	0.02	0.018	<0.01	<0.01	4.84	0.02	0.002	0.32	4.22
632850	Rock	0.39	<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	0.02	0.21	<0.02	0.01	<0.001	<0.01	<0.01	22.09	0.03	<0.001	10.90	0.18



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**

Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: December 22, 2010

Page: 3 of 3 **Part** 2

CERTIFICATE OF ANALYSIS

WHI10000677.1

	Method	7TD	7TD	7TD	7TD	G8SG	7TD.1
	Analyte	Na	K	W	S	SG	Pb
	Unit	%	%	%	%		%
	MDL	0.01	0.01	0.01	0.05	0	0.02
632831	Drill Core	<0.01	0.55	<0.01	1.70	2.20	
632832	Drill Core	<0.01	0.07	<0.01	4.93	2.58	
632833	Drill Core	<0.01	0.18	<0.01	4.68	2.48	
632834	Drill Core	<0.01	0.35	<0.01	1.94	2.44	
632835	Drill Core	<0.01	0.15	<0.01	0.33	2.45	
632836	Drill Core	<0.01	0.19	<0.01	2.79	2.50	
632837	Drill Core	<0.01	0.12	<0.01	1.01	2.49	
632838	Drill Core	<0.01	0.31	<0.01	3.80	2.46	
632839	Drill Core	<0.01	0.53	<0.01	0.57	2.27	
632840	Drill Core	<0.01	0.48	<0.01	2.09	2.29	
632841	Drill Core	<0.01	0.48	<0.01	2.05	2.30	
632842	Drill Core	<0.01	0.62	<0.01	3.76	2.23	
632843	Drill Core	<0.01	0.78	<0.01	1.24	2.12	
632844	Drill Core	<0.01	1.50	<0.01	1.98	2.53	
632845	Drill Core	<0.01	1.16	<0.01	1.47	2.57	
632846	Drill Core	<0.01	1.59	<0.01	2.29	2.34	
632847	Drill Core	<0.01	2.44	<0.01	3.09	1.96	
632848	Drill Core	<0.01	3.07	<0.01	3.13	2.05	
632849	Rock Pulp	1.75	1.29	<0.01	3.46	N.A.	
632850	Rock	0.01	0.02	<0.01	0.13	2.62	



Acme Analytical Laboratories (Vancouver) Ltd.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: Selwyn Resources Ltd.

Suite 700 - 509 Richards Street

Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: December 22, 2010

Page: 1 of 2 Part 1

QUALITY CONTROL REPORT

WHI10000677.1

	Method Analyte Unit MDL	WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD
		Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg	Al
		kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%	%
		0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01	0.01
Pulp Duplicates																					
632819	Drill Core	2.70	<0.001	0.004	>10	18.29	11	0.001	<0.001	0.01	1.76	<0.02	<0.01	0.108	<0.01	<0.01	8.56	0.06	<0.001	0.02	0.09
REP 632819	QC																				
632822	Drill Core	1.54	<0.001	0.005	>10	25.04	13	<0.001	<0.001	<0.01	0.74	<0.02	<0.01	0.130	<0.01	<0.01	1.55	0.10	<0.001	<0.01	0.06
REP 632822	QC		<0.001	0.004	>10	24.79	13	<0.001	<0.001	<0.01	0.74	<0.02	<0.01	0.127	<0.01	<0.01	1.54	0.10	<0.001	<0.01	0.06
632848	Drill Core	2.97	0.005	0.011	0.03	<0.01	<2	0.025	<0.001	0.01	2.81	<0.02	<0.01	<0.001	<0.01	<0.01	2.97	0.38	0.011	0.39	4.05
REP 632848	QC		0.005	0.011	0.03	<0.01	<2	0.025	<0.001	0.01	2.88	<0.02	<0.01	<0.001	<0.01	<0.01	3.03	0.39	0.011	0.40	4.13
Core Reject Duplicates																					
632807	Drill Core	0.66	<0.001	0.001	0.13	1.16	<2	0.004	<0.001	0.01	0.66	<0.02	<0.01	0.004	<0.01	<0.01	5.38	0.09	<0.001	0.08	0.57
DUP 632807	QC		<0.001	0.002	0.12	1.14	<2	0.004	<0.001	0.01	0.64	<0.02	<0.01	0.004	<0.01	<0.01	5.33	0.09	<0.001	0.08	0.57
632842	Drill Core	0.54	0.007	0.021	0.08	5.48	7	0.014	<0.001	0.01	1.21	<0.02	<0.01	0.018	<0.01	<0.01	4.38	0.09	0.003	0.11	0.91
DUP 632842	QC		0.006	0.020	0.08	5.34	6	0.013	<0.001	0.01	1.07	<0.02	<0.01	0.018	<0.01	<0.01	4.46	0.10	0.002	0.11	0.91
Reference Materials																					
STD CCU-1C	Standard																				
STD CZN-3	Standard																				
STD OREAS131A	Standard		<0.001	0.032	1.69	2.84	31	0.002	0.002	0.17	5.81	<0.02	<0.01	0.008	<0.01	<0.01	5.29	0.06	0.002	3.13	4.54
STD OREAS131A	Standard		<0.001	0.032	1.76	2.93	31	0.003	0.002	0.18	5.92	<0.02	<0.01	0.008	<0.01	<0.01	5.46	0.06	0.002	3.13	4.61
STD OREAS131A	Standard		<0.001	0.032	1.69	2.88	32	0.002	0.002	0.17	5.82	<0.02	<0.01	0.008	<0.01	<0.01	5.33	0.06	0.002	3.14	4.67
STD PTC-1A	Standard																				
STD R4T	Standard		0.064	0.510	1.59	3.43	88	0.356	0.042	0.09	24.07	<0.02	0.02	0.019	0.01	<0.01	2.19	0.05	0.019	1.43	3.98
STD R4T	Standard		0.064	0.516	1.61	3.50	89	0.357	0.042	0.09	24.79	<0.02	0.02	0.019	0.01	<0.01	2.21	0.05	0.018	1.44	3.91
STD R4T	Standard		0.064	0.507	1.55	3.39	86	0.351	0.041	0.09	23.82	<0.02	0.02	0.018	0.01	<0.01	2.19	0.05	0.017	1.41	3.99
STD SARM 71	Standard																				
STD SU-1B	Standard		<0.001	1.177	<0.02	0.03	7	1.980	0.068	0.07	25.17	<0.02	0.03	<0.001	<0.01	<0.01	2.23	0.06	0.031	1.81	4.39
STD SU-1B	Standard		<0.001	1.164	<0.02	0.03	7	1.932	0.066	0.07	25.29	<0.02	0.03	<0.001	<0.01	<0.01	2.19	0.07	0.031	1.75	4.28
STD SU-1B	Standard		<0.001	1.188	<0.02	0.03	7	1.964	0.067	0.07	25.16	<0.02	0.03	<0.001	<0.01	<0.01	2.25	0.06	0.027	1.81	4.45
STD R4T Expected			0.062	0.502	1.518	3.376	86	0.339	0.039	0.086	24.07	0.0087	0.0185	0.018	0.0138	0.0018	2.166	0.045	0.018	1.384	3.897
STD OREAS131A Expected			0.001	0.0322	1.72	2.83	30.9	0.0027	0.0023	0.1722	5.8166	0.0082	0.0028	0.0081	0.0047	0.001	5.286	0.0536	0.0025	3.1182	4.6057
STD SU-1B Expected			0.0004	1.185	0.0058	0.0235	6.4	1.97	0.0672	0.0703	25.54	0.00025	0.03	0.0003	0.00002	0.0003	2.21	0.06	0.032	1.79	4.39



Acme Analytical Laboratories (Vancouver) Ltd.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: Selwyn Resources Ltd.

Suite 700 - 509 Richards Street

Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: December 22, 2010

Page: 1 of 2 **Part** 2

QUALITY CONTROL REPORT

WHI10000677.1

Method		7TD	7TD	7TD	7TD	G8SG	7TD.1
Analyte		Na	K	W	S	SG	Pb
Unit		%	%	%	%		%
MDL		0.01	0.01	0.01	0.05	0	0.02
Pulp Duplicates							
632819	Drill Core	<0.01	0.04	<0.01	13.91	3.30	18.28
REP 632819	QC						18.29
632822	Drill Core	<0.01	0.03	<0.01	16.35	3.39	18.05
REP 632822	QC	<0.01	0.03	<0.01	15.92		
632848	Drill Core	<0.01	3.07	<0.01	3.13	2.05	
REP 632848	QC	<0.01	3.15	<0.01	3.21		
Core Reject Duplicates							
632807	Drill Core	<0.01	0.31	<0.01	1.21	2.40	
DUP 632807	QC	0.01	0.32	<0.01	1.23	2.40	
632842	Drill Core	<0.01	0.62	<0.01	3.76	2.23	
DUP 632842	QC	<0.01	0.68	<0.01	3.65	2.23	
Reference Materials							
STD CCU-1C	Standard						0.36
STD CZN-3	Standard						0.13
STD OREAS131A	Standard	0.15	3.41	<0.01	4.73		
STD OREAS131A	Standard	0.15	3.48	<0.01	4.99		
STD OREAS131A	Standard	0.15	3.45	<0.01	5.01		
STD PTC-1A	Standard						0.03
STD R4T	Standard	0.93	1.19	<0.01	12.21		
STD R4T	Standard	0.95	1.21	<0.01	13.93		
STD R4T	Standard	0.92	1.18	<0.01	14.07		
STD SARM 71	Standard						<0.02
STD SU-1B	Standard	1.70	0.62	<0.01	8.28		
STD SU-1B	Standard	1.69	0.63	<0.01	9.65		
STD SU-1B	Standard	1.71	0.63	<0.01	11.68		
STD R4T Expected		0.9	1.153	0.00016	12.9903		
STD OREAS131A Expected		0.1501	3.1584	0.0005	4.8		
STD SU-1B Expected		1.662	0.6	0.0007	8.76		



Acme Analytical Laboratories (Vancouver) Ltd.
1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: December 22, 2010

Page: 2 of 2 Part 1

QUALITY CONTROL REPORT

WHI10000677.1

		WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD
		Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg
		kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%
		0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01
STD CZN-3 Expected																				
STD CCU-1C Expected																				
STD PTC-1A Expected																				
BLK	Blank	<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	<0.01	<0.01	<0.02	<0.01	<0.001	<0.01	<0.01	<0.01	<0.01	<0.001	<0.01	<0.01
BLK	Blank	<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	<0.01	<0.01	<0.02	<0.01	<0.001	<0.01	<0.01	<0.01	<0.01	<0.001	<0.01	<0.01
BLK	Blank	<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	<0.01	<0.01	<0.02	<0.01	<0.001	<0.01	<0.01	<0.01	<0.01	<0.001	<0.01	<0.01
BLK	Blank																			
Prep Wash																				
G1	Prep Blank	<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	0.07	2.37	<0.02	0.07	<0.001	<0.01	<0.01	2.16	0.08	<0.001	0.59	6.53
G1	Prep Blank	<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	0.07	2.33	<0.02	0.07	<0.001	<0.01	<0.01	2.22	0.08	<0.001	0.59	6.51



Acme Analytical Laboratories (Vancouver) Ltd.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: **Selwyn Resources Ltd.**

Suite 700 - 509 Richards Street

Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: December 22, 2010

Page: 2 of 2 **Part** 2

QUALITY CONTROL REPORT

WHI10000677.1

		7TD Na %	7TD K %	7TD W %	7TD S %	G8SG SG 0	7TD.1 Pb %
		0.01	0.01	0.01	0.05	0	0.02
STD CZN-3 Expected							0.113
STD CCU-1C Expected							0.34
STD PTC-1A Expected							0.05
BLK	Blank	<0.01	<0.01	<0.01	<0.05		
BLK	Blank	<0.01	<0.01	<0.01	<0.05		
BLK	Blank	<0.01	<0.01	<0.01	<0.05		
BLK	Blank						<0.02
Prep Wash							
G1	Prep Blank	2.71	2.94	<0.01	<0.05	2.63	
G1	Prep Blank	2.75	2.95	<0.01	<0.05	2.62	



1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: Selwyn Resources Ltd.

Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Submitted By: Jason K. Dunning

Receiving Lab: Canada-Whitehorse

Received: December 03, 2010

Report Date: December 17, 2010

Page: 1 of 5

CERTIFICATE OF ANALYSIS

WHI10000675.1

CLIENT JOB INFORMATION

Project: Selwyn Project
Shipment ID:
P.O. Number 1117
Number of Samples: 120

SAMPLE DISPOSAL

STOR-PLP Store After 90 days Invoice for Storage
STOR-RJT Store After 90 days Invoice for Storage

Acme does not accept responsibility for samples left at the laboratory after 90 days without prior written instructions for sample storage or return.

Invoice To: Selwyn Resources Ltd.
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6
Canada

CC:

SAMPLE PREPARATION AND ANALYTICAL PROCEDURES

Method Code	Number of Samples	Code Description	Test Wgt (g)	Report Status	Lab
R200-250	116	Crush split and pulverize 250g drill core to 200 mesh			WHI
7TD2	120	4 Acid digestion ICP-ES analysis.	0.5	Completed	VAN
G812	120	Specific Gravity on Pulp		Completed	VAN

ADDITIONAL COMMENTS



This report supersedes all previous preliminary and final reports with this file number dated prior to the date on this certificate. Signature indicates final approval; preliminary reports are unsigned and should be used for reference only.
All results are considered the confidential property of the client. Acme assumes the liabilities for actual cost of analysis only.
** asterisk indicates that an analytical result could not be provided due to unusually high levels of interference from other elements.



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: December 17, 2010

Page: 2 of 5 Part 1

CERTIFICATE OF ANALYSIS

WHI10000675.1

	Method Analyte Unit MDL	WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD
		Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg
		kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%
		0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01
635901	Drill Core	3.62	<0.001	0.006	0.07	0.67	<2	0.006	<0.001	0.02	2.18	<0.02	<0.01	0.002	<0.01	<0.01	9.46	0.54	0.002	0.13
635902	Drill Core	3.20	0.001	0.004	<0.02	0.43	<2	0.010	<0.001	<0.01	0.81	<0.02	<0.01	0.002	<0.01	<0.01	1.95	0.67	0.003	0.16
635903	Drill Core	0.94	0.005	0.007	0.04	0.32	3	0.015	<0.001	<0.01	1.64	<0.02	<0.01	<0.001	<0.01	<0.01	0.89	0.19	0.004	0.18
635904	Drill Core	1.31	0.004	0.002	0.15	0.07	<2	0.009	<0.001	<0.01	0.84	<0.02	<0.01	<0.001	<0.01	<0.01	1.09	0.03	0.002	0.12
635905	Drill Core	1.65	0.004	0.007	1.60	3.78	3	0.009	<0.001	0.01	4.26	<0.02	<0.01	0.019	<0.01	<0.01	1.05	0.03	0.002	0.11
635906	Drill Core	1.61	0.002	0.006	3.69	8.49	3	0.006	<0.001	0.02	4.02	<0.02	<0.01	0.027	<0.01	<0.01	3.59	0.03	0.001	0.06
635907	Drill Core	3.03	0.003	0.007	2.03	8.14	3	0.009	<0.001	0.01	6.85	<0.02	<0.01	0.026	<0.01	<0.01	0.57	0.03	0.002	0.07
635908	Drill Core	0.84	<0.001	<0.001	0.18	1.03	<2	0.002	<0.001	0.10	0.94	<0.02	0.02	0.001	<0.01	<0.01	28.78	0.03	<0.001	0.13
635909	Drill Core	1.32	0.003	0.007	3.02	8.74	3	0.011	<0.001	0.02	5.77	<0.02	<0.01	0.021	<0.01	<0.01	1.15	0.05	0.002	0.10
635910	Drill Core	1.40	0.003	0.007	2.24	6.47	3	0.008	<0.001	0.02	11.18	<0.02	<0.01	0.017	<0.01	<0.01	4.59	0.05	0.001	0.08
635911	Drill Core	1.15	0.002	0.004	1.31	5.05	<2	0.006	<0.001	0.02	11.21	<0.02	<0.01	0.013	<0.01	<0.01	5.43	0.04	<0.001	0.06
635912	Drill Core	2.23	0.001	0.002	1.02	1.54	<2	0.003	<0.001	0.02	1.69	<0.02	<0.01	0.003	<0.01	<0.01	8.98	0.04	<0.001	0.06
635913	Drill Core	0.81	<0.001	<0.001	0.06	0.05	<2	0.001	<0.001	0.07	0.36	<0.02	0.02	<0.001	<0.01	<0.01	27.41	0.01	<0.001	0.07
635914	Drill Core	3.97	0.002	0.002	0.46	1.88	<2	0.004	<0.001	<0.01	1.14	<0.02	<0.01	0.005	<0.01	<0.01	3.35	0.04	<0.001	0.05
635915	Drill Core	2.06	0.004	0.004	0.19	1.61	<2	0.010	<0.001	<0.01	1.88	<0.02	<0.01	0.003	<0.01	<0.01	2.90	0.05	0.002	0.10
635916	Drill Core	1.30	0.007	0.003	0.36	0.65	<2	0.012	<0.001	<0.01	1.75	<0.02	<0.01	0.001	<0.01	<0.01	2.67	0.03	0.002	0.11
635917	Drill Core	1.38	0.002	0.004	0.45	2.07	<2	0.005	<0.001	0.05	2.60	<0.02	0.01	0.006	<0.01	<0.01	20.03	0.02	<0.001	0.09
635918	Drill Core	0.72	0.004	0.015	6.46	13.10	4	0.008	<0.001	0.04	5.34	<0.02	<0.01	0.038	<0.01	<0.01	10.06	0.07	0.001	0.08
635919	Drill Core	2.97	<0.001	<0.001	0.19	0.78	<2	0.003	<0.001	0.07	0.90	<0.02	0.02	0.003	<0.01	<0.01	24.86	0.04	<0.001	0.11
635920	Rock	0.43	<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	0.02	0.13	<0.02	0.01	<0.001	<0.01	<0.01	19.83	0.02	<0.001	10.54
635921	Drill Core	1.61	0.001	0.004	0.99	4.24	<2	0.008	<0.001	0.03	3.42	<0.02	<0.01	0.009	<0.01	<0.01	5.50	0.10	0.002	0.14
635922	Drill Core	1.94	0.002	0.005	1.02	8.05	2	0.005	<0.001	0.05	5.81	<0.02	0.01	0.019	<0.01	<0.01	20.63	0.03	0.001	0.10
635923	Drill Core	2.58	0.002	0.003	2.23	7.19	4	0.004	<0.001	0.04	3.13	<0.02	0.01	0.021	<0.01	<0.01	20.69	0.03	<0.001	0.07
635924	Drill Core	2.73	0.001	0.003	1.43	3.29	<2	0.006	<0.001	0.03	2.10	<0.02	<0.01	0.009	<0.01	<0.01	13.85	0.05	0.002	0.09
635925	Drill Core	3.47	0.001	0.004	6.91	21.48	5	0.003	<0.001	<0.01	1.09	<0.02	<0.01	0.071	<0.01	<0.01	0.68	0.03	<0.001	0.02
635926	Drill Core	1.69	<0.001	0.004	6.42	20.92	5	0.002	<0.001	0.01	1.85	<0.02	<0.01	0.063	<0.01	<0.01	3.05	0.03	<0.001	0.03
635927	Drill Core	2.14	0.002	0.003	2.13	4.99	2	0.004	<0.001	0.03	1.80	<0.02	<0.01	0.014	<0.01	<0.01	11.72	0.04	<0.001	0.08
635928	Drill Core	2.41	<0.001	<0.001	0.32	0.50	<2	0.002	<0.001	0.07	1.51	<0.02	0.02	0.001	<0.01	<0.01	27.53	0.05	<0.001	0.12
635929	Drill Core	0.36	0.002	0.004	1.20	3.01	<2	0.007	<0.001	0.03	1.64	<0.02	0.01	0.008	<0.01	<0.01	12.54	0.05	0.002	0.13
635930	Drill Core	1.39	<0.001	<0.001	0.09	0.50	<2	0.002	<0.001	0.07	0.84	<0.02	0.02	0.001	<0.01	<0.01	29.39	0.03	<0.001	0.10



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: December 17, 2010

Page: 2 of 5 **Part** 2

CERTIFICATE OF ANALYSIS

WHI10000675.1

	Method	7TD	7TD	7TD	7TD	G8SG
	Analyte	Na	K	W	S	SG
	Unit	%	%	%	%	
	MDL	0.01	0.01	0.01	0.05	0
635901	Drill Core	<0.01	0.53	<0.01	2.75	2.40
635902	Drill Core	<0.01	0.89	<0.01	0.99	2.21
635903	Drill Core	<0.01	1.06	<0.01	1.89	2.14
635904	Drill Core	<0.01	0.73	<0.01	0.84	2.23
635905	Drill Core	<0.01	0.72	<0.01	6.89	2.47
635906	Drill Core	<0.01	0.40	<0.01	9.31	2.57
635907	Drill Core	<0.01	0.44	<0.01	12.61	2.56
635908	Drill Core	0.01	0.11	<0.01	1.65	2.45
635909	Drill Core	<0.01	0.58	<0.01	11.44	2.35
635910	Drill Core	<0.01	0.45	<0.01	16.61	2.60
635911	Drill Core	<0.01	0.35	<0.01	15.83	2.69
635912	Drill Core	<0.01	0.21	<0.01	2.73	2.41
635913	Drill Core	<0.01	0.06	<0.01	0.42	2.49
635914	Drill Core	<0.01	0.26	<0.01	2.23	2.35
635915	Drill Core	<0.01	0.65	<0.01	2.94	2.26
635916	Drill Core	<0.01	0.90	<0.01	2.34	2.19
635917	Drill Core	<0.01	0.24	<0.01	4.33	2.46
635918	Drill Core	<0.01	0.44	<0.01	14.02	2.66
635919	Drill Core	<0.01	0.16	<0.01	1.50	2.51
635920	Rock	<0.01	0.02	<0.01	<0.05	2.60
635921	Drill Core	<0.01	0.62	<0.01	6.37	2.49
635922	Drill Core	<0.01	0.24	<0.01	12.00	2.66
635923	Drill Core	<0.01	0.20	<0.01	8.12	2.62
635924	Drill Core	<0.01	0.36	<0.01	4.29	2.40
635925	Drill Core	<0.01	0.10	<0.01	12.84	2.84
635926	Drill Core	<0.01	0.13	<0.01	13.40	2.78
635927	Drill Core	<0.01	0.28	<0.01	4.86	2.53
635928	Drill Core	<0.01	0.14	<0.01	2.09	2.45
635929	Drill Core	<0.01	0.55	<0.01	3.67	2.35
635930	Drill Core	<0.01	0.06	<0.01	1.24	2.48



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: December 17, 2010

Page: 3 of 5 Part 1

CERTIFICATE OF ANALYSIS

WHI10000675.1

	Method Analyte Unit MDL	WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD
		Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg	Al
		kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%	%
		0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01	0.01
635931	Rock Pulp	0.06	<0.001	0.692	6.29	7.00	72	0.001	<0.001	0.10	4.87	<0.02	0.02	0.019	0.05	<0.01	1.37	0.02	0.001	0.26	5.38
635932	Drill Core	2.71	0.002	0.003	1.69	5.15	2	0.004	<0.001	0.04	2.61	<0.02	0.01	0.013	<0.01	<0.01	20.80	0.04	0.001	0.08	0.46
635933	Drill Core	0.65	<0.001	0.001	1.15	4.88	<2	0.004	<0.001	0.02	1.82	<0.02	<0.01	0.014	<0.01	<0.01	6.50	0.05	<0.001	0.07	0.57
635934	Drill Core	0.62	<0.001	0.001	1.47	6.69	<2	0.003	<0.001	0.02	1.70	<0.02	<0.01	0.021	<0.01	<0.01	7.43	0.05	0.001	0.06	0.46
635935	Drill Core	1.81	<0.001	0.002	0.84	4.62	<2	0.002	<0.001	0.02	1.49	<0.02	<0.01	0.013	<0.01	<0.01	5.01	0.03	<0.001	0.05	0.36
635936	Drill Core	0.84	0.003	0.008	2.60	8.40	2	0.008	<0.001	0.05	6.70	<0.02	<0.01	0.018	<0.01	<0.01	14.50	0.07	0.001	0.08	0.61
635937	Drill Core	2.00	0.001	0.002	1.35	5.99	<2	0.003	<0.001	0.03	1.76	<0.02	<0.01	0.013	<0.01	<0.01	14.35	0.03	<0.001	0.07	0.37
635938	Drill Core	1.35	0.001	0.002	0.64	2.42	<2	0.002	<0.001	0.02	0.94	<0.02	<0.01	0.007	<0.01	<0.01	10.87	0.03	<0.001	0.06	0.37
635939	Drill Core	0.90	<0.001	0.002	0.51	1.65	<2	0.003	<0.001	0.03	1.28	<0.02	0.01	0.004	<0.01	<0.01	17.63	0.03	<0.001	0.08	0.38
635940	Drill Core	0.90	<0.001	<0.001	0.18	0.13	<2	0.001	<0.001	0.04	0.38	<0.02	0.02	<0.001	<0.01	<0.01	25.79	0.03	<0.001	0.09	0.33
635941	Drill Core	0.90	<0.001	<0.001	0.35	0.38	<2	0.002	<0.001	0.04	0.59	<0.02	0.02	<0.001	<0.01	<0.01	25.99	0.03	0.001	0.09	0.32
635942	Drill Core	1.11	0.003	0.004	1.10	5.20	<2	0.007	<0.001	0.01	1.81	<0.02	<0.01	0.012	<0.01	<0.01	4.06	0.08	0.002	0.10	1.06
635943	Drill Core	0.79	0.001	0.003	2.16	3.00	<2	0.004	<0.001	0.04	1.37	<0.02	0.01	0.007	<0.01	<0.01	21.97	0.18	0.001	0.11	0.60
635944	Drill Core	0.86	0.002	0.005	1.28	4.16	<2	0.005	<0.001	0.03	1.25	<0.02	<0.01	0.009	<0.01	<0.01	15.14	0.11	0.003	0.10	0.69
635945	Drill Core	1.53	<0.001	0.002	0.23	2.00	<2	0.003	<0.001	0.02	0.60	<0.02	<0.01	0.004	<0.01	<0.01	14.09	0.03	<0.001	0.07	0.38
635946	Drill Core	1.05	<0.001	<0.001	0.08	0.01	<2	0.003	<0.001	0.04	0.70	<0.02	0.02	<0.001	<0.01	<0.01	26.75	0.03	<0.001	0.10	0.44
635947	Drill Core	2.41	0.001	0.003	0.02	<0.01	<2	0.004	<0.001	0.03	1.84	<0.02	0.02	<0.001	<0.01	<0.01	23.61	0.04	0.001	0.11	0.68
635948	Drill Core	1.13	<0.001	0.001	0.07	<0.01	<2	0.004	<0.001	0.04	1.11	<0.02	0.01	<0.001	<0.01	<0.01	19.91	0.04	0.001	0.12	0.69
635949	Drill Core	1.31	0.002	0.004	0.10	0.10	<2	0.007	<0.001	0.03	2.64	<0.02	<0.01	<0.001	<0.01	<0.01	10.01	0.04	0.002	0.13	0.87
635950	Rock	0.36	<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	0.01	0.30	<0.02	0.01	<0.001	<0.01	<0.01	20.32	0.03	<0.001	10.82	0.22
635951	Drill Core	1.31	0.001	0.002	0.04	0.06	<2	0.004	<0.001	0.02	0.64	<0.02	<0.01	<0.001	<0.01	<0.01	7.07	0.04	0.001	0.08	0.50
635952	Drill Core	1.33	0.001	0.002	0.11	0.62	<2	0.004	<0.001	<0.01	2.32	<0.02	<0.01	0.002	<0.01	<0.01	1.88	0.02	0.001	0.10	0.53
635953	Drill Core	1.45	<0.001	<0.001	0.20	0.07	<2	0.003	<0.001	0.01	0.48	<0.02	<0.01	<0.001	<0.01	<0.01	6.20	0.03	<0.001	0.07	0.46
635954	Drill Core	1.31	0.002	0.005	0.47	0.63	<2	0.007	<0.001	0.03	1.97	<0.02	<0.01	0.002	<0.01	<0.01	11.10	0.36	0.002	0.13	0.83
635955	Drill Core	0.91	<0.001	0.005	0.22	1.03	<2	0.004	<0.001	0.05	2.48	<0.02	0.02	0.003	<0.01	<0.01	22.67	0.13	<0.001	0.12	0.23
635956	Drill Core	1.62	0.003	0.005	0.42	0.36	<2	0.005	<0.001	0.05	1.88	<0.02	0.02	0.002	<0.01	<0.01	24.31	0.18	0.002	0.09	0.30
635957	Drill Core	2.38	0.004	0.007	0.24	0.80	<2	0.006	<0.001	0.03	0.75	<0.02	0.01	0.002	<0.01	<0.01	15.69	0.28	0.003	0.09	0.55
635958	Drill Core	1.78	0.004	0.008	0.17	0.49	<2	0.008	<0.001	0.01	1.56	<0.02	<0.01	<0.001	<0.01	<0.01	9.24	0.28	0.003	0.08	0.65
635959	Drill Core	0.98	0.008	0.010	0.41	1.22	3	0.014	<0.001	0.02	1.30	<0.02	0.01	0.004	<0.01	<0.01	10.85	0.32	0.006	0.15	1.15
635960	Rock Pulp	0.06	<0.001	0.479	1.41	2.89	17	<0.001	<0.001	0.44	2.59	<0.02	0.02	0.018	<0.01	<0.01	4.64	0.02	<0.001	0.32	4.05



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: December 17, 2010

Page: 3 of 5 **Part** 2

CERTIFICATE OF ANALYSIS

WHI10000675.1

	Method	7TD	7TD	7TD	7TD	G8SG
	Analyte	Na	K	W	S	SG
	Unit	%	%	%	%	
	MDL	0.01	0.01	0.01	0.05	0
635931	Rock Pulp	2.28	1.33	<0.01	5.19	N.A.
635932	Drill Core	<0.01	0.23	<0.01	6.24	2.52
635933	Drill Core	<0.01	0.30	<0.01	5.09	2.48
635934	Drill Core	<0.01	0.25	<0.01	6.05	2.55
635935	Drill Core	<0.01	0.19	<0.01	4.26	2.54
635936	Drill Core	<0.01	0.34	<0.01	13.29	2.67
635937	Drill Core	<0.01	0.20	<0.01	5.69	2.60
635938	Drill Core	<0.01	0.22	<0.01	2.50	2.50
635939	Drill Core	<0.01	0.20	<0.01	2.45	2.41
635940	Drill Core	<0.01	0.18	<0.01	0.51	2.45
635941	Drill Core	<0.01	0.17	<0.01	0.91	2.40
635942	Drill Core	<0.01	0.56	<0.01	5.02	2.40
635943	Drill Core	<0.01	0.30	<0.01	3.64	2.49
635944	Drill Core	<0.01	0.38	<0.01	3.87	2.43
635945	Drill Core	<0.01	0.20	<0.01	1.70	2.41
635946	Drill Core	<0.01	0.23	<0.01	0.90	2.40
635947	Drill Core	<0.01	0.33	<0.01	2.21	2.40
635948	Drill Core	<0.01	0.35	<0.01	1.32	2.39
635949	Drill Core	<0.01	0.48	<0.01	3.29	2.34
635950	Rock	<0.01	0.03	<0.01	<0.05	2.60
635951	Drill Core	<0.01	0.25	<0.01	0.56	2.33
635952	Drill Core	<0.01	0.27	<0.01	2.96	2.43
635953	Drill Core	<0.01	0.24	<0.01	0.41	2.37
635954	Drill Core	<0.01	0.50	<0.01	2.69	2.34
635955	Drill Core	<0.01	0.13	<0.01	3.52	2.42
635956	Drill Core	<0.01	0.17	<0.01	2.60	2.39
635957	Drill Core	<0.01	0.31	<0.01	1.26	2.34
635958	Drill Core	<0.01	0.36	<0.01	2.01	2.43
635959	Drill Core	<0.01	0.63	<0.01	2.23	2.23
635960	Rock Pulp	1.67	1.23	<0.01	3.46	N.A.



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: December 17, 2010

Page: 4 of 5 Part 1

CERTIFICATE OF ANALYSIS

WHI10000675.1

	Method Analyte Unit MDL	WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD
		Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg	Al
		kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%	%
		0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01	0.01
635961	Drill Core	1.48	0.008	0.013	0.07	1.01	<2	0.013	<0.001	0.01	1.73	<0.02	<0.01	0.003	<0.01	<0.01	6.03	0.08	0.004	0.12	1.06
635962	Drill Core	0.96	0.002	0.004	0.28	0.59	<2	0.006	<0.001	0.03	2.37	<0.02	0.02	0.002	<0.01	<0.01	16.36	0.13	0.001	0.10	0.52
635963	Drill Core	1.38	0.002	0.004	1.06	4.64	4	0.006	<0.001	0.02	2.45	<0.02	<0.01	0.013	<0.01	<0.01	5.70	0.05	0.001	0.10	0.66
635964	Drill Core	1.48	0.004	0.008	0.06	0.14	<2	0.021	0.001	0.02	3.20	<0.02	0.01	<0.001	<0.01	<0.01	10.46	1.15	0.012	0.37	3.29
635965	Drill Core	0.94	0.001	0.003	0.05	0.09	<2	0.004	<0.001	0.02	1.40	<0.02	0.01	<0.001	<0.01	<0.01	12.37	0.08	0.002	0.14	0.73
635966	Drill Core	1.43	0.001	0.003	<0.02	0.02	<2	0.005	<0.001	<0.01	1.23	<0.02	<0.01	<0.001	<0.01	<0.01	5.71	1.21	0.003	0.11	1.23
635967	Drill Core	2.79	0.003	0.008	<0.02	0.18	<2	0.012	<0.001	0.01	2.08	<0.02	<0.01	<0.001	<0.01	<0.01	3.49	0.85	0.004	0.22	2.02
635968	Drill Core	1.63	0.003	0.004	0.19	0.72	<2	0.008	<0.001	0.01	1.71	<0.02	<0.01	0.003	<0.01	<0.01	1.94	0.06	0.002	0.11	1.10
635969	Drill Core	1.47	0.003	0.008	1.36	8.88	2	0.007	<0.001	0.01	4.75	<0.02	<0.01	0.029	<0.01	<0.01	0.85	0.04	0.001	0.09	0.90
635970	Drill Core	0.57	0.002	0.006	1.20	6.16	<2	0.007	<0.001	0.02	7.16	<0.02	<0.01	0.021	<0.01	<0.01	2.04	0.04	0.002	0.09	0.85
635971	Drill Core	0.66	0.002	0.006	1.32	5.73	2	0.006	<0.001	0.01	7.38	<0.02	<0.01	0.020	<0.01	<0.01	1.98	0.04	0.002	0.09	0.86
635972	Drill Core	0.87	<0.001	0.005	5.02	12.59	3	0.003	<0.001	<0.01	4.93	<0.02	<0.01	0.053	<0.01	<0.01	0.55	0.01	<0.001	0.04	0.33
635973	Drill Core	2.19	0.003	0.006	1.18	7.12	2	0.009	<0.001	0.02	5.53	<0.02	<0.01	0.019	<0.01	<0.01	2.75	0.05	0.002	0.09	0.89
635974	Drill Core	0.90	0.006	0.008	1.35	11.17	3	0.011	<0.001	0.02	5.65	<0.02	<0.01	0.026	<0.01	<0.01	2.89	0.08	0.002	0.11	1.28
635975	Drill Core	1.15	0.001	0.002	0.67	1.99	<2	0.005	<0.001	0.02	1.35	<0.02	<0.01	0.007	<0.01	<0.01	9.80	0.07	0.001	0.09	0.64
635976	Drill Core	1.45	0.001	0.002	0.20	1.53	<2	0.003	<0.001	0.01	1.29	<0.02	<0.01	0.004	<0.01	<0.01	5.99	0.03	<0.001	0.06	0.41
635977	Drill Core	1.14	<0.001	0.001	<0.02	0.13	<2	0.002	<0.001	0.02	0.41	<0.02	<0.01	<0.001	<0.01	<0.01	14.00	0.03	<0.001	0.04	0.25
635978	Drill Core	0.85	0.001	0.002	0.27	2.00	<2	0.003	<0.001	0.02	0.71	<0.02	<0.01	0.006	<0.01	<0.01	14.42	0.04	<0.001	0.06	0.40
635979	Drill Core	1.42	0.002	0.002	0.21	1.71	<2	0.005	<0.001	<0.01	0.86	<0.02	<0.01	0.005	<0.01	<0.01	0.66	0.06	0.001	0.07	0.61
635980	Rock	0.40	<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	0.02	0.12	<0.02	0.01	<0.001	<0.01	<0.01	22.08	0.04	<0.001	11.07	0.12
635981	Drill Core	1.12	0.001	0.002	0.03	0.37	<2	0.004	<0.001	<0.01	0.58	<0.02	<0.01	0.001	<0.01	<0.01	0.93	0.04	0.001	0.08	0.56
635982	Drill Core	1.59	0.007	0.005	0.06	0.93	<2	0.015	<0.001	<0.01	2.21	<0.02	<0.01	0.003	<0.01	<0.01	0.91	0.06	0.003	0.15	1.71
635983	Drill Core	1.56	0.008	0.004	0.04	0.97	<2	0.015	<0.001	<0.01	1.73	<0.02	<0.01	0.003	<0.01	<0.01	0.51	0.05	0.003	0.14	1.73
635984	Drill Core	1.32	0.003	0.010	2.06	9.79	2	0.008	<0.001	0.04	5.20	<0.02	<0.01	0.026	<0.01	<0.01	7.59	0.06	0.001	0.08	0.67
635985	Drill Core	1.51	<0.001	<0.001	0.34	1.54	<2	0.001	<0.001	0.07	0.85	<0.02	0.02	0.005	<0.01	<0.01	31.16	0.06	<0.001	0.10	0.14
635986	Drill Core	1.70	<0.001	0.002	0.59	1.97	<2	0.003	<0.001	0.03	1.15	<0.02	0.01	0.006	<0.01	<0.01	22.65	0.05	0.001	0.09	0.47
635987	Drill Core	1.37	0.002	0.004	1.15	4.93	<2	0.006	<0.001	0.04	3.48	<0.02	0.01	0.014	<0.01	<0.01	20.81	0.05	0.001	0.12	0.64
635988	Drill Core	1.89	0.001	0.003	0.81	4.10	<2	0.003	<0.001	0.04	2.56	<0.02	0.02	0.010	<0.01	<0.01	25.91	0.03	0.001	0.09	0.34
635989	Drill Core	1.26	0.001	0.003	0.72	4.89	<2	0.005	<0.001	0.02	2.07	<0.02	<0.01	0.012	<0.01	<0.01	3.43	0.07	<0.001	0.09	0.63
635990	Rock Pulp	0.06	<0.001	0.671	6.10	7.04	70	<0.001	0.001	0.10	5.06	<0.02	0.02	0.019	0.02	<0.01	1.41	0.02	0.001	0.26	5.20



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: December 17, 2010

Page: 4 of 5 **Part** 2

CERTIFICATE OF ANALYSIS

WHI10000675.1

	Method	7TD	7TD	7TD	7TD	G8SG
	Analyte	Na	K	W	S	SG
	Unit	%	%	%	%	
	MDL	0.01	0.01	0.01	0.05	0
635961	Drill Core	<0.01	0.57	<0.01	2.51	2.30
635962	Drill Core	<0.01	0.29	<0.01	3.25	2.52
635963	Drill Core	<0.01	0.35	<0.01	5.19	2.52
635964	Drill Core	<0.01	1.80	<0.01	3.90	2.13
635965	Drill Core	<0.01	0.64	<0.01	1.51	2.47
635966	Drill Core	<0.01	0.93	<0.01	1.22	2.48
635967	Drill Core	<0.01	1.28	<0.01	2.32	2.32
635968	Drill Core	<0.01	0.72	<0.01	2.17	2.35
635969	Drill Core	<0.01	0.57	<0.01	9.77	2.57
635970	Drill Core	<0.01	0.54	<0.01	11.49	2.62
635971	Drill Core	<0.01	0.55	<0.01	11.50	2.59
635972	Drill Core	<0.01	0.20	<0.01	12.19	2.86
635973	Drill Core	<0.01	0.59	<0.01	9.97	2.44
635974	Drill Core	<0.01	0.92	<0.01	12.06	2.51
635975	Drill Core	<0.01	0.39	<0.01	2.57	2.31
635976	Drill Core	<0.01	0.23	<0.01	2.13	2.46
635977	Drill Core	<0.01	0.13	<0.01	0.46	2.46
635978	Drill Core	<0.01	0.24	<0.01	1.82	2.45
635979	Drill Core	<0.01	0.38	<0.01	1.54	2.36
635980	Rock	0.01	0.02	<0.01	0.11	2.59
635981	Drill Core	<0.01	0.33	<0.01	0.53	2.31
635982	Drill Core	<0.01	1.16	<0.01	2.86	2.07
635983	Drill Core	<0.01	1.27	<0.01	2.36	2.06
635984	Drill Core	<0.01	0.42	<0.01	11.14	2.58
635985	Drill Core	<0.01	0.07	<0.01	1.91	2.51
635986	Drill Core	<0.01	0.30	<0.01	2.43	2.48
635987	Drill Core	<0.01	0.37	<0.01	6.62	2.54
635988	Drill Core	<0.01	0.19	<0.01	4.59	2.53
635989	Drill Core	<0.01	0.37	<0.01	4.60	2.37
635990	Rock Pulp	2.30	1.40	<0.01	5.42	N.A.



Acme Analytical Laboratories (Vancouver) Ltd.
1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: December 17, 2010

Page: 5 of 5 Part 1

CERTIFICATE OF ANALYSIS

WHI10000675.1

	Method Analyte Unit MDL	WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD
		Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg	Al
		kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%	%
		0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01	0.01
635991	Drill Core	1.61	0.001	<0.001	0.06	0.77	<2	0.004	<0.001	0.03	0.96	<0.02	0.01	0.002	<0.01	<0.01	17.31	0.03	0.001	0.09	0.50
635992	Drill Core	1.71	0.001	0.003	3.02	13.62	3	0.003	<0.001	0.04	1.91	<0.02	0.01	0.033	<0.01	<0.01	23.07	0.03	<0.001	0.06	0.23
635993	Drill Core	1.99	0.002	0.008	4.98	27.97	6	0.007	<0.001	0.03	4.76	<0.02	<0.01	0.058	<0.01	<0.01	5.83	0.06	0.001	0.08	0.52
635994	Drill Core	1.45	0.002	0.003	0.61	2.29	<2	0.005	<0.001	0.04	4.26	<0.02	0.01	0.006	<0.01	<0.01	19.64	0.05	0.001	0.10	0.54
635995	Drill Core	1.84	0.001	0.002	1.19	2.67	<2	0.004	<0.001	0.02	1.65	<0.02	<0.01	0.007	<0.01	<0.01	9.00	0.05	<0.001	0.09	0.57
635996	Drill Core	1.66	0.001	0.004	2.55	14.26	2	0.002	<0.001	0.02	1.58	<0.02	<0.01	0.033	<0.01	<0.01	13.75	0.02	<0.001	0.04	0.21
635997	Drill Core	1.03	0.002	0.009	3.09	27.56	6	0.007	<0.001	0.03	3.88	<0.02	<0.01	0.056	<0.01	<0.01	5.14	0.05	0.001	0.07	0.45
635998	Drill Core	1.53	0.002	0.002	0.85	3.00	<2	0.006	<0.001	0.02	2.05	<0.02	<0.01	0.007	<0.01	<0.01	8.69	0.04	0.001	0.09	0.67
635999	Drill Core	0.91	0.003	0.003	1.26	3.46	<2	0.008	<0.001	0.02	2.07	<0.02	<0.01	0.009	<0.01	<0.01	7.68	0.08	0.001	0.12	0.94
636000	Drill Core	0.51	0.002	0.002	0.42	1.90	<2	0.005	<0.001	0.02	0.86	<0.02	0.01	0.005	<0.01	<0.01	9.84	0.04	0.001	0.08	0.60
634151	Drill Core	0.56	0.001	0.002	1.80	2.55	2	0.003	<0.001	0.02	0.95	<0.02	<0.01	0.006	<0.01	<0.01	12.96	0.04	<0.001	0.06	0.34
634152	Drill Core	1.19	0.001	0.002	1.81	2.35	2	0.004	<0.001	0.02	1.06	<0.02	<0.01	0.006	<0.01	<0.01	11.70	0.05	<0.001	0.07	0.44
634153	Drill Core	0.81	0.003	0.002	0.20	0.63	3	0.007	<0.001	0.02	0.71	<0.02	<0.01	0.001	<0.01	<0.01	8.55	0.13	0.002	0.13	1.09
634154	Drill Core	1.16	0.003	0.005	1.65	4.85	3	0.008	<0.001	0.03	1.62	<0.02	0.01	0.012	<0.01	<0.01	16.89	0.37	0.002	0.13	0.78
634155	Drill Core	2.89	0.001	0.002	0.03	0.02	<2	0.004	<0.001	0.03	1.13	<0.02	0.02	<0.001	<0.01	<0.01	24.59	0.06	0.001	0.13	0.72
634156	Drill Core	3.30	0.001	0.003	0.02	0.04	<2	0.005	<0.001	0.03	1.09	<0.02	0.01	<0.001	<0.01	<0.01	22.15	0.06	0.001	0.13	0.81
634157	Drill Core	2.20	<0.001	0.003	0.10	0.04	<2	0.003	<0.001	0.05	1.71	<0.02	0.02	<0.001	<0.01	<0.01	28.27	0.02	<0.001	0.10	0.39
634158	Drill Core	1.22	0.002	0.003	0.11	0.13	<2	0.007	<0.001	0.03	1.40	<0.02	0.01	<0.001	<0.01	<0.01	21.78	0.04	0.001	0.12	0.83
634159	Drill Core	1.43	0.001	0.002	0.24	0.76	<2	0.005	<0.001	<0.01	0.70	<0.02	<0.01	0.002	<0.01	<0.01	1.10	0.03	<0.001	0.07	0.52
634160	Rock	0.38	<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	0.02	0.08	<0.02	0.01	<0.001	<0.01	<0.01	20.95	0.04	<0.001	10.68	0.10
634161	Drill Core	0.91	0.003	0.011	0.59	1.13	3	0.009	<0.001	0.04	0.94	<0.02	0.01	0.003	<0.01	<0.01	13.92	0.09	0.002	0.16	0.89
634162	Drill Core	1.37	0.001	0.008	0.15	1.05	<2	0.005	<0.001	0.05	4.65	<0.02	0.01	0.002	<0.01	<0.01	21.49	0.16	<0.001	0.92	0.31
634163	Drill Core	0.86	0.002	0.004	0.30	0.51	<2	0.006	<0.001	0.03	0.58	<0.02	0.01	0.002	<0.01	<0.01	18.91	0.12	<0.001	0.07	0.40
634164	Drill Core	0.67	0.008	0.019	0.21	0.62	3	0.013	<0.001	0.02	0.97	<0.02	0.01	0.002	<0.01	<0.01	14.12	1.12	0.003	0.14	0.99
634165	Drill Core	2.12	0.003	0.008	0.14	1.01	3	0.007	<0.001	0.03	1.20	<0.02	0.02	0.003	<0.01	<0.01	21.30	0.25	0.001	0.10	0.55
634166	Drill Core	1.98	0.001	0.003	<0.02	<0.01	<2	0.007	<0.001	0.03	2.48	<0.02	0.02	<0.001	<0.01	<0.01	20.33	1.29	0.003	0.35	2.91
634167	Drill Core	1.24	0.012	0.014	0.04	0.02	7	0.034	0.001	0.01	5.30	<0.02	<0.01	<0.001	<0.01	<0.01	3.87	0.25	0.012	0.42	4.02
634168	Drill Core	0.71	0.007	0.011	0.09	0.81	5	0.025	0.001	0.02	3.76	<0.02	<0.01	0.005	<0.01	<0.01	5.24	0.15	0.009	0.36	3.22
634169	Drill Core	1.36	0.008	0.008	0.04	0.57	6	0.029	0.001	<0.01	2.78	<0.02	<0.01	0.004	<0.01	<0.01	1.90	0.33	0.012	0.42	4.13
634170	Rock Pulp	0.06	<0.001	0.486	1.45	2.95	20	<0.001	<0.001	0.43	2.69	<0.02	0.02	0.018	<0.01	<0.01	5.04	0.02	0.001	0.33	4.23



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: December 17, 2010

Page: 5 of 5 **Part** 2

CERTIFICATE OF ANALYSIS

WHI10000675.1

	Method	7TD	7TD	7TD	7TD	G8SG
	Analyte	Na	K	W	S	SG
	Unit	%	%	%	%	
	MDL	0.01	0.01	0.01	0.05	0
635991	Drill Core	<0.01	0.29	<0.01	1.45	2.36
635992	Drill Core	<0.01	0.12	<0.01	9.48	2.69
635993	Drill Core	<0.01	0.29	<0.01	19.10	2.95
635994	Drill Core	<0.01	0.32	<0.01	6.12	2.54
635995	Drill Core	<0.01	0.34	<0.01	3.26	2.49
635996	Drill Core	<0.01	0.11	<0.01	9.24	2.75
635997	Drill Core	<0.01	0.26	<0.01	17.46	2.93
635998	Drill Core	<0.01	0.40	<0.01	3.87	2.45
635999	Drill Core	<0.01	0.56	<0.01	4.09	2.41
636000	Drill Core	<0.01	0.38	<0.01	1.84	2.40
634151	Drill Core	<0.01	0.20	<0.01	2.57	2.55
634152	Drill Core	<0.01	0.26	<0.01	2.58	2.51
634153	Drill Core	<0.01	0.70	<0.01	0.98	2.29
634154	Drill Core	0.42	0.43	<0.01	4.56	2.48
634155	Drill Core	0.16	0.38	<0.01	1.32	2.40
634156	Drill Core	<0.01	0.45	<0.01	1.26	2.39
634157	Drill Core	<0.01	0.19	<0.01	2.07	2.45
634158	Drill Core	<0.01	0.46	<0.01	1.66	2.35
634159	Drill Core	<0.01	0.30	<0.01	1.02	2.42
634160	Rock	<0.01	0.02	<0.01	<0.05	2.56
634161	Drill Core	<0.01	0.50	<0.01	1.65	2.36
634162	Drill Core	<0.01	0.17	<0.01	6.18	2.65
634163	Drill Core	<0.01	0.21	<0.01	0.90	2.44
634164	Drill Core	<0.01	0.53	<0.01	1.38	2.31
634165	Drill Core	<0.01	0.30	<0.01	1.85	2.44
634166	Drill Core	<0.01	1.52	<0.01	2.75	2.56
634167	Drill Core	<0.01	2.63	<0.01	6.11	1.99
634168	Drill Core	<0.01	2.06	<0.01	4.56	2.08
634169	Drill Core	<0.01	2.81	<0.01	3.31	1.86
634170	Rock Pulp	1.76	1.26	<0.01	3.34	N.A.



Acme Analytical Laboratories (Vancouver) Ltd.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: **Selwyn Resources Ltd.**

Suite 700 - 509 Richards Street

Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: December 17, 2010

Page: 1 of 2 Part 1

QUALITY CONTROL REPORT

WHI10000675.1

	Method Analyte Unit MDL	WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD
		Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg	Al
		kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%	%
		0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01	0.01
Pulp Duplicates																					
635919	Drill Core	2.97	<0.001	<0.001	0.19	0.78	<2	0.003	<0.001	0.07	0.90	<0.02	0.02	0.003	<0.01	<0.01	24.86	0.04	<0.001	0.11	0.29
REP 635919	QC		<0.001	<0.001	0.17	0.75	<2	0.003	<0.001	0.07	0.91	<0.02	0.02	0.002	<0.01	<0.01	24.84	0.04	<0.001	0.14	0.30
635937	Drill Core	2.00	0.001	0.002	1.35	5.99	<2	0.003	<0.001	0.03	1.76	<0.02	<0.01	0.013	<0.01	<0.01	14.35	0.03	<0.001	0.07	0.37
REP 635937	QC		<0.001	0.002	1.35	6.08	<2	0.003	<0.001	0.03	1.76	<0.02	<0.01	0.015	<0.01	<0.01	14.34	0.03	<0.001	0.07	0.37
635985	Drill Core	1.51	<0.001	<0.001	0.34	1.54	<2	0.001	<0.001	0.07	0.85	<0.02	0.02	0.005	<0.01	<0.01	31.16	0.06	<0.001	0.10	0.14
REP 635985	QC		<0.001	0.001	0.35	1.50	<2	0.001	<0.001	0.07	0.83	<0.02	0.02	0.005	<0.01	<0.01	30.23	0.06	<0.001	0.10	0.14
634164	Drill Core	0.67	0.008	0.019	0.21	0.62	3	0.013	<0.001	0.02	0.97	<0.02	0.01	0.002	<0.01	<0.01	14.12	1.12	0.003	0.14	0.99
REP 634164	QC		0.008	0.018	0.21	0.61	3	0.013	<0.001	0.02	0.97	<0.02	0.01	0.002	<0.01	<0.01	13.95	1.12	0.003	0.14	0.98
Core Reject Duplicates																					
635928	Drill Core	2.41	<0.001	<0.001	0.32	0.50	<2	0.002	<0.001	0.07	1.51	<0.02	0.02	0.001	<0.01	<0.01	27.53	0.05	<0.001	0.12	0.27
DUP 635928	QC		<0.001	<0.001	0.31	0.50	<2	0.002	<0.001	0.07	1.52	<0.02	0.02	0.001	<0.01	<0.01	27.39	0.05	<0.001	0.12	0.29
635963	Drill Core	1.38	0.002	0.004	1.06	4.64	4	0.006	<0.001	0.02	2.45	<0.02	<0.01	0.013	<0.01	<0.01	5.70	0.05	0.001	0.10	0.66
DUP 635963	QC		0.002	0.004	1.08	4.51	4	0.007	<0.001	0.02	2.50	<0.02	<0.01	0.013	<0.01	<0.01	5.84	0.06	0.001	0.10	0.67
635998	Drill Core	1.53	0.002	0.002	0.85	3.00	<2	0.006	<0.001	0.02	2.05	<0.02	<0.01	0.007	<0.01	<0.01	8.69	0.04	0.001	0.09	0.67
DUP 635998	QC		0.002	0.002	0.93	3.01	<2	0.006	<0.001	0.02	2.08	<0.02	<0.01	0.007	<0.01	<0.01	8.81	0.04	<0.001	0.09	0.67
Reference Materials																					
STD OREAS131A	Standard		<0.001	0.032	1.74	2.82	31	0.003	0.002	0.17	5.76	<0.02	<0.01	0.007	<0.01	<0.01	5.26	0.05	0.002	3.12	4.64
STD OREAS131A	Standard		<0.001	0.032	1.69	2.87	31	0.003	0.002	0.17	5.88	<0.02	<0.01	0.008	<0.01	<0.01	5.38	0.06	0.002	3.11	4.58
STD OREAS131A	Standard		<0.001	0.032	1.70	2.81	31	0.002	0.002	0.17	5.78	<0.02	<0.01	0.009	<0.01	<0.01	5.33	0.05	0.002	3.14	4.64
STD OREAS131A	Standard		<0.001	0.033	1.75	2.87	32	0.003	0.002	0.17	5.87	<0.02	<0.01	0.008	<0.01	<0.01	5.40	0.05	0.002	3.16	4.64
STD R4T	Standard		0.064	0.514	1.58	3.43	90	0.357	0.040	0.09	24.07	<0.02	0.02	0.018	0.02	<0.01	2.17	0.04	0.019	1.42	4.00
STD R4T	Standard		0.064	0.509	1.56	3.45	88	0.351	0.041	0.09	24.59	<0.02	0.02	0.019	0.02	<0.01	2.19	0.05	0.019	1.44	3.92
STD R4T	Standard		0.063	0.516	1.55	3.47	91	0.353	0.041	0.09	23.99	<0.02	0.02	0.019	0.02	<0.01	2.26	0.04	0.019	1.43	4.02
STD R4T	Standard		0.064	0.508	1.59	3.44	90	0.356	0.041	0.09	24.20	<0.02	0.02	0.019	0.01	<0.01	2.20	0.05	0.018	1.42	3.98
STD SU-1B	Standard		<0.001	1.259	<0.02	0.02	7	2.109	0.068	0.08	25.81	<0.02	0.03	<0.001	<0.01	<0.01	2.27	0.06	0.032	1.85	4.56
STD SU-1B	Standard		<0.001	1.156	<0.02	0.02	7	1.899	0.065	0.07	25.38	<0.02	0.03	<0.001	<0.01	<0.01	2.19	0.07	0.030	1.77	4.29
STD SU-1B	Standard		<0.001	1.188	<0.02	0.03	6	1.963	0.067	0.07	25.02	<0.02	0.03	0.002	<0.01	<0.01	2.32	0.06	0.034	1.82	4.48
STD SU-1B	Standard		<0.001	1.204	<0.02	0.03	7	2.013	0.069	0.07	25.60	<0.02	0.03	<0.001	<0.01	<0.01	2.25	0.06	0.032	1.82	4.46



Acme Analytical Laboratories (Vancouver) Ltd.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: Selwyn Resources Ltd.

Suite 700 - 509 Richards Street

Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: December 17, 2010

Page: 1 of 2 **Part** 2

QUALITY CONTROL REPORT

WHI10000675.1

Method		7TD	7TD	7TD	7TD	G8SG
Analyte		Na	K	W	S	SG
Unit		%	%	%	%	%
MDL		0.01	0.01	0.01	0.05	0
Pulp Duplicates						
635919	Drill Core	<0.01	0.16	<0.01	1.50	2.51
REP 635919	QC	<0.01	0.16	<0.01	1.56	
635937	Drill Core	<0.01	0.20	<0.01	5.69	2.60
REP 635937	QC	<0.01	0.20	<0.01	5.57	
635985	Drill Core	<0.01	0.07	<0.01	1.91	2.51
REP 635985	QC	<0.01	0.07	<0.01	1.85	
634164	Drill Core	<0.01	0.53	<0.01	1.38	2.31
REP 634164	QC	<0.01	0.54	<0.01	1.39	
Core Reject Duplicates						
635928	Drill Core	<0.01	0.14	<0.01	2.09	2.45
DUP 635928	QC	<0.01	0.15	<0.01	2.15	2.45
635963	Drill Core	<0.01	0.35	<0.01	5.19	2.52
DUP 635963	QC	<0.01	0.35	<0.01	5.52	2.50
635998	Drill Core	<0.01	0.40	<0.01	3.87	2.45
DUP 635998	QC	<0.01	0.40	<0.01	3.87	2.41
Reference Materials						
STD OREAS131A	Standard	0.15	3.30	<0.01	4.89	
STD OREAS131A	Standard	0.15	3.49	<0.01	4.90	
STD OREAS131A	Standard	0.15	3.37	<0.01	5.18	
STD OREAS131A	Standard	0.15	3.38	<0.01	4.94	
STD R4T	Standard	0.89	1.14	<0.01	13.03	
STD R4T	Standard	0.94	1.27	<0.01	12.35	
STD R4T	Standard	0.93	1.16	<0.01	13.26	
STD R4T	Standard	0.92	1.18	<0.01	12.30	
STD SU-1B	Standard	1.72	0.61	<0.01	9.03	
STD SU-1B	Standard	1.72	0.63	<0.01	8.76	
STD SU-1B	Standard	1.74	0.62	<0.01	8.89	
STD SU-1B	Standard	1.74	0.62	<0.01	8.72	



Acme Analytical Laboratories (Vancouver) Ltd.
1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: December 17, 2010

Page: 2 of 2 Part 1

QUALITY CONTROL REPORT

WHI10000675.1

		WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD
		Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg	Al
		kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%	%
		0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01	0.01
STD R4T Expected			0.062	0.502	1.518	3.376	86	0.339	0.039	0.086	24.07	0.0087	0.0185	0.018	0.0138	0.0018	2.166	0.045	0.018	1.384	3.897
STD OREAS131A Expected			0.001	0.0322	1.72	2.83	30.9	0.0027	0.0023	0.1722	5.8166	0.0082	0.0028	0.0081	0.0047	0.001	5.286	0.0536	0.0025	3.1182	4.6057
STD SU-1B Expected			0.0004	1.185	0.0058	0.0235	6.4	1.97	0.0672	0.0703	25.54	0.00025	0.03	0.0003	0.00002	0.0003	2.21	0.06	0.032	1.79	4.39
BLK	Blank		<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	<0.01	<0.01	<0.02	<0.01	<0.001	<0.01	<0.01	<0.01	<0.01	<0.001	<0.01	<0.01
BLK	Blank		<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	<0.01	<0.01	<0.02	<0.01	<0.001	<0.01	<0.01	<0.01	<0.01	<0.001	<0.01	<0.01
BLK	Blank		<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	<0.01	<0.01	<0.02	<0.01	<0.001	<0.01	<0.01	<0.01	<0.01	<0.001	<0.01	<0.01
BLK	Blank		<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	<0.01	<0.01	<0.02	<0.01	<0.001	<0.01	<0.01	<0.01	<0.01	<0.001	<0.01	<0.01
Prep Wash																					
G1	Prep Blank		<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	0.08	2.42	<0.02	0.08	<0.001	<0.01	<0.01	2.40	0.08	<0.001	0.65	8.53
G1	Prep Blank		<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	0.08	2.40	<0.02	0.08	<0.001	<0.01	<0.01	2.43	0.08	<0.001	0.68	8.33



Acme Analytical Laboratories (Vancouver) Ltd.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: **Selwyn Resources Ltd.**

Suite 700 - 509 Richards Street

Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: December 17, 2010

Page: 2 of 2 **Part** 2

QUALITY CONTROL REPORT

WHI10000675.1

		7TD Na %	7TD K %	7TD W %	7TD S %	G8SG SG %
		0.01	0.01	0.01	0.05	0
STD R4T Expected		0.9	1.153	0.00016	12.9903	
STD OREAS131A Expected		0.1501	3.1584	0.0005	4.8	
STD SU-1B Expected		1.662	0.6	0.0007	8.76	
BLK	Blank	<0.01	<0.01	<0.01	<0.05	
BLK	Blank	<0.01	<0.01	<0.01	<0.05	
BLK	Blank	<0.01	<0.01	<0.01	<0.05	
BLK	Blank	<0.01	<0.01	<0.01	<0.05	
Prep Wash						
G1	Prep Blank	2.80	3.17	<0.01	0.07	2.63
G1	Prep Blank	2.74	3.03	<0.01	<0.05	2.60



1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: Selwyn Resources Ltd.

Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Submitted By: Jason K. Dunning

Receiving Lab: Canada-Whitehorse

Received: December 02, 2010

Report Date: December 10, 2010

Page: 1 of 2

CERTIFICATE OF ANALYSIS

WHI10000673.1

CLIENT JOB INFORMATION

Project: Selwyn Project
Shipment ID:
P.O. Number 1107
Number of Samples: 16

SAMPLE DISPOSAL

STOR-PLP Store After 90 days Invoice for Storage
STOR-RJT Store After 90 days Invoice for Storage

Acme does not accept responsibility for samples left at the laboratory after 90 days without prior written instructions for sample storage or return.

Invoice To: Selwyn Resources Ltd.
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6
Canada

CC:

SAMPLE PREPARATION AND ANALYTICAL PROCEDURES

Method Code	Number of Samples	Code Description	Test Wgt (g)	Report Status	Lab
R200-250	16	Crush split and pulverize 250g drill core to 200 mesh			WHI
7TD2	16	4 Acid digestion ICP-ES analysis.	0.5	Completed	VAN
G812	16	Specific Gravity on Pulp		Completed	VAN

ADDITIONAL COMMENTS



This report supersedes all previous preliminary and final reports with this file number dated prior to the date on this certificate. Signature indicates final approval; preliminary reports are unsigned and should be used for reference only.
All results are considered the confidential property of the client. Acme assumes the liabilities for actual cost of analysis only.
"*" asterisk indicates that an analytical result could not be provided due to unusually high levels of interference from other elements.



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: December 10, 2010

Page: 2 of 2 Part 1

CERTIFICATE OF ANALYSIS

WHI10000673.1

	Method Analyte Unit MDL	WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD
		Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg	Al
		kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%	%
		0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01	0.01
632151	Drill Core	2.08	<0.001	0.005	0.02	0.22	<2	0.015	<0.001	<0.01	1.72	<0.02	<0.01	0.002	<0.01	<0.01	7.18	2.39	0.008	0.78	4.00
632152	Drill Core	1.06	<0.001	0.013	0.36	4.30	4	0.007	<0.001	0.02	1.52	<0.02	0.01	0.015	<0.01	<0.01	13.35	1.24	0.005	0.47	2.28
632153	Drill Core	1.08	<0.001	0.014	1.49	16.06	11	0.003	<0.001	0.01	2.54	<0.02	<0.01	0.056	<0.01	<0.01	4.77	0.03	0.002	0.13	0.62
632154	Drill Core	0.79	<0.001	0.005	0.10	0.26	<2	0.010	<0.001	0.02	2.12	<0.02	0.01	<0.001	<0.01	<0.01	12.22	1.38	0.007	0.55	3.06
632155	Drill Core	1.99	0.001	0.007	<0.02	0.21	<2	0.011	<0.001	0.01	1.92	<0.02	<0.01	0.002	<0.01	<0.01	6.69	1.25	0.007	0.57	3.50
632156	Drill Core	2.03	<0.001	0.007	<0.02	<0.01	<2	0.010	<0.001	0.01	1.98	<0.02	0.01	<0.001	<0.01	<0.01	11.31	1.39	0.005	0.42	2.98
632157	Drill Core	2.03	<0.001	0.010	<0.02	<0.01	<2	0.012	<0.001	<0.01	2.58	<0.02	<0.01	<0.001	<0.01	<0.01	5.97	1.39	0.006	0.35	3.09
632158	Drill Core	2.17	0.001	0.006	<0.02	<0.01	<2	0.010	<0.001	0.01	1.58	<0.02	0.01	0.002	<0.01	<0.01	8.44	1.01	0.005	0.27	2.68
632159	Drill Core	0.64	0.003	0.004	<0.02	0.02	<2	0.012	<0.001	0.01	1.91	<0.02	0.01	0.002	<0.01	<0.01	4.80	0.60	0.007	0.45	2.97
632160	Drill Core	0.78	0.005	0.007	<0.02	1.05	2	0.006	<0.001	0.04	1.18	<0.02	0.02	0.006	<0.01	<0.01	20.23	0.09	0.001	0.19	0.57
632161	Drill Core	0.59	0.006	0.007	<0.02	0.91	<2	0.007	<0.001	0.05	1.33	<0.02	0.02	0.006	<0.01	<0.01	20.62	0.09	0.001	0.19	0.57
632162	Drill Core	1.59	0.002	0.006	<0.02	0.02	<2	0.004	<0.001	0.04	1.12	<0.02	0.03	0.002	<0.01	<0.01	29.66	0.13	0.001	0.18	0.21
632163	Drill Core	2.18	0.005	0.014	0.06	0.37	2	0.012	<0.001	0.02	3.28	<0.02	0.02	0.001	<0.01	<0.01	12.72	0.32	0.003	0.13	0.82
632164	Drill Core	1.55	0.011	0.016	0.03	0.55	2	0.019	<0.001	<0.01	1.00	<0.02	<0.01	0.004	<0.01	<0.01	3.90	0.28	0.004	0.20	1.52
632165	Drill Core	1.89	0.010	0.016	0.02	0.11	2	0.023	<0.001	<0.01	1.41	<0.02	<0.01	0.003	<0.01	<0.01	4.59	0.92	0.006	0.22	1.75
632166	Drill Core	2.59	<0.001	0.002	<0.02	<0.01	<2	0.003	<0.001	0.04	1.96	<0.02	0.02	0.002	<0.01	<0.01	22.12	0.07	0.003	0.33	1.99



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: December 10, 2010

Page: 2 of 2 **Part** 2

CERTIFICATE OF ANALYSIS

WHI10000673.1

	Method	7TD	7TD	7TD	7TD	G8SG
	Analyte	Na	K	W	S	SG
	Unit	%	%	%	%	
	MDL	0.01	0.01	0.01	0.05	0
632151	Drill Core	0.03	2.48	<0.01	1.78	2.12
632152	Drill Core	0.01	1.40	<0.01	3.73	2.33
632153	Drill Core	<0.01	0.39	<0.01	11.27	2.79
632154	Drill Core	0.02	1.88	<0.01	2.35	2.18
632155	Drill Core	0.01	2.02	<0.01	2.05	2.14
632156	Drill Core	<0.01	1.67	<0.01	2.17	2.19
632157	Drill Core	<0.01	1.77	<0.01	2.80	2.14
632158	Drill Core	<0.01	1.75	<0.01	1.61	2.22
632159	Drill Core	<0.01	1.72	<0.01	1.92	2.28
632160	Drill Core	<0.01	0.33	<0.01	1.89	2.38
632161	Drill Core	<0.01	0.33	<0.01	1.98	2.36
632162	Drill Core	<0.01	0.12	<0.01	1.32	2.39
632163	Drill Core	<0.01	0.46	<0.01	4.05	2.30
632164	Drill Core	<0.01	0.81	<0.01	1.30	2.04
632165	Drill Core	<0.01	0.98	<0.01	1.57	2.05
632166	Drill Core	<0.01	1.07	<0.01	2.22	2.53



Acme Analytical Laboratories (Vancouver) Ltd.
1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: December 10, 2010

Page: 1 of 1 Part 1

QUALITY CONTROL REPORT

WHI10000673.1

	Method Analyte Unit MDL	WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD
		Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg	Al
		kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%	%
		0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01	0.01
REP 632164	QC		0.010	0.015	0.03	0.53	3	0.019	<0.001	<0.01	0.96	<0.02	<0.01	0.002	<0.01	<0.01	3.73	0.27	0.005	0.19	1.45
Core Reject Duplicates																					
632164	Drill Core	1.55	0.011	0.016	0.03	0.55	2	0.019	<0.001	<0.01	1.00	<0.02	<0.01	0.004	<0.01	<0.01	3.90	0.28	0.004	0.20	1.52
DUP 632164	QC		0.010	0.015	0.02	0.54	2	0.018	<0.001	<0.01	0.93	<0.02	<0.01	0.003	<0.01	<0.01	4.28	0.25	0.004	0.19	1.41
Reference Materials																					
STD OREAS131A	Standard		<0.001	0.033	1.74	2.90	31	0.002	0.002	0.17	5.84	<0.02	<0.01	0.010	<0.01	<0.01	5.31	0.05	0.002	3.18	4.71
STD R4T	Standard		0.064	0.521	1.59	3.47	90	0.357	0.040	0.09	24.39	<0.02	0.02	0.023	0.02	<0.01	2.19	0.04	0.019	1.43	4.02
STD SU-1B	Standard		<0.001	1.218	<0.02	0.03	8	2.041	0.068	0.07	25.58	<0.02	0.03	0.002	<0.01	<0.01	2.26	0.06	0.032	1.82	4.43
STD R4T Expected			0.062	0.502	1.518	3.376	86	0.339	0.039	0.086	24.07	0.0087	0.0185	0.018	0.0138	0.0018	2.166	0.045	0.018	1.384	3.897
STD OREAS131A Expected			0.001	0.0322	1.72	2.83	30.9	0.0027	0.0023	0.1722	5.8166	0.0082	0.0028	0.0081	0.0047	0.001	5.286	0.0536	0.0025	3.1182	4.6057
STD SU-1B Expected			0.0004	1.185	0.0058	0.0235	6.4	1.97	0.0672	0.0703	25.54	0.00025	0.03	0.0003	0.00002	0.0003	2.21	0.06	0.032	1.79	4.39
BLK	Blank		<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	<0.01	<0.01	<0.02	<0.01	<0.001	<0.01	<0.01	<0.01	<0.01	<0.001	<0.01	<0.01
Prep Wash																					
G1	Prep Blank		<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	0.07	2.28	<0.02	0.07	0.002	<0.01	<0.01	2.32	0.07	<0.001	0.60	7.24
G1	Prep Blank		<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	0.07	2.22	<0.02	0.07	0.001	<0.01	<0.01	2.31	0.07	<0.001	0.56	7.12



Acme Analytical Laboratories (Vancouver) Ltd.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: **Selwyn Resources Ltd.**

Suite 700 - 509 Richards Street

Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: December 10, 2010

Page: 1 of 1 **Part** 2

QUALITY CONTROL REPORT

WHI10000673.1

	Method	7TD	7TD	7TD	7TD	G8SG
Analyte		Na	K	W	S	SG
Unit		%	%	%	%	
MDL		0.01	0.01	0.01	0.05	0
REP 632164	QC	<0.01	0.78	<0.01	1.22	
Core Reject Duplicates						
632164	Drill Core	<0.01	0.81	<0.01	1.30	2.04
DUP 632164	QC	<0.01	0.77	<0.01	1.22	2.05
Reference Materials						
STD OREAS131A	Standard	0.15	3.29	<0.01	4.85	
STD R4T	Standard	0.93	1.17	<0.01	12.47	
STD SU-1B	Standard	1.73	0.62	<0.01	8.34	
STD R4T Expected		0.9	1.153	0.00016	12.9903	
STD OREAS131A Expected		0.1501	3.1584	0.0005	4.8	
STD SU-1B Expected		1.662	0.6	0.0007	8.76	
BLK	Blank	<0.01	<0.01	<0.01	<0.05	
Prep Wash						
G1	Prep Blank	2.68	2.53	<0.01	<0.05	2.68
G1	Prep Blank	2.72	2.40	<0.01	<0.05	2.62



1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: Selwyn Resources Ltd.

Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Submitted By: Jason K. Dunning

Receiving Lab: Canada-Whitehorse

Received: November 30, 2010

Report Date: December 23, 2010

Page: 1 of 5

CERTIFICATE OF ANALYSIS

WHI10000669.1

CLIENT JOB INFORMATION

Project: Selwyn Project
Shipment ID:
P.O. Number 1107
Number of Samples: 91

SAMPLE DISPOSAL

STOR-PLP Store After 90 days Invoice for Storage
STOR-RJT Store After 90 days Invoice for Storage

Acme does not accept responsibility for samples left at the laboratory after 90 days without prior written instructions for sample storage or return.

Invoice To: Selwyn Resources Ltd.
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6
Canada

CC:

SAMPLE PREPARATION AND ANALYTICAL PROCEDURES

Method Code	Number of Samples	Code Description	Test Wgt (g)	Report Status	Lab
R200-250	88	Crush split and pulverize 250g drill core to 200 mesh			WHI
7TD2	91	4 Acid digestion ICP-ES analysis.	0.5	Completed	VAN
G812	91	Specific Gravity on Pulp		Completed	VAN
7TD.1	6	4 Acid digestion ICP-ES analysis	0.1	Completed	VAN

ADDITIONAL COMMENTS



This report supersedes all previous preliminary and final reports with this file number dated prior to the date on this certificate. Signature indicates final approval; preliminary reports are unsigned and should be used for reference only.
All results are considered the confidential property of the client. Acme assumes the liabilities for actual cost of analysis only.
** asterisk indicates that an analytical result could not be provided due to unusually high levels of interference from other elements.



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: December 23, 2010

Page: 2 of 5 Part 1

CERTIFICATE OF ANALYSIS

WHI10000669.1

	Method Analyte Unit MDL	WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD
		Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg	Al
		kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%	%
		0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01	0.01
635301	Drill Core	3.04	0.001	0.003	<0.02	0.26	<2	0.007	<0.001	0.03	0.66	<0.02	<0.01	<0.001	<0.01	<0.01	10.28	0.72	0.002	0.15	1.09
635302	Drill Core	3.27	0.003	0.003	0.05	0.34	<2	0.010	<0.001	<0.01	1.06	<0.02	<0.01	<0.001	<0.01	<0.01	1.48	0.44	0.003	0.16	1.62
635303	Drill Core	2.30	0.005	0.010	1.65	7.10	3	0.011	<0.001	0.02	5.73	<0.02	<0.01	0.027	<0.01	<0.01	3.91	0.05	0.002	0.12	1.32
635304	Drill Core	3.84	0.001	0.003	0.95	5.15	<2	0.004	<0.001	0.04	2.78	<0.02	0.01	0.024	<0.01	<0.01	16.44	0.04	0.001	0.13	0.68
635305	Drill Core	2.67	0.006	0.010	1.03	6.59	<2	0.010	<0.001	0.02	4.06	<0.02	<0.01	0.018	<0.01	<0.01	2.79	0.05	0.002	0.10	1.16
635306	Drill Core	4.19	<0.001	<0.001	0.29	0.47	<2	0.001	<0.001	0.07	2.43	<0.02	0.02	0.001	<0.01	<0.01	26.68	0.03	<0.001	0.11	0.16
635307	Drill Core	4.08	0.001	0.004	0.89	5.39	<2	0.005	<0.001	0.04	2.60	<0.02	0.01	0.013	<0.01	<0.01	15.88	0.05	0.001	0.09	0.55
635308	Drill Core	0.79	<0.001	<0.001	0.59	2.72	<2	0.001	<0.001	0.04	1.15	<0.02	0.02	0.008	<0.01	<0.01	26.39	0.04	<0.001	0.09	0.21
635309	Drill Core	2.04	0.002	0.004	1.35	4.43	2	0.007	<0.001	0.03	4.84	<0.02	0.01	0.010	<0.01	<0.01	12.00	0.07	0.002	0.12	0.92
635310	Drill Core	1.36	0.001	0.004	9.95	22.06	8	0.003	<0.001	0.01	1.38	<0.02	<0.01	0.090	<0.01	<0.01	1.01	0.04	<0.001	0.03	0.23
635311	Drill Core	1.59	0.001	0.004	8.10	18.43	6	0.003	<0.001	0.01	1.38	<0.02	<0.01	0.074	<0.01	<0.01	5.95	0.04	<0.001	0.04	0.22
635312	Drill Core	2.29	0.001	0.004	5.93	12.67	5	0.004	<0.001	0.01	3.56	<0.02	<0.01	0.046	<0.01	<0.01	6.60	0.03	<0.001	0.03	0.23
635313	Drill Core	1.16	0.003	0.005	0.12	0.15	<2	0.010	<0.001	0.02	5.12	<0.02	<0.01	<0.001	<0.01	<0.01	6.64	0.03	0.001	0.07	0.59
635314	Drill Core	3.41	0.002	0.006	0.71	1.42	<2	0.008	<0.001	0.01	3.12	<0.02	<0.01	0.003	<0.01	<0.01	5.00	0.27	0.002	0.09	0.78
635315	Drill Core	0.47	<0.001	0.001	<0.02	0.08	<2	<0.001	<0.001	0.15	0.38	<0.02	0.02	<0.001	<0.01	<0.01	33.43	0.10	<0.001	0.07	0.06
635316	Drill Core	3.56	0.004	0.010	0.21	0.83	<2	0.006	<0.001	0.03	1.15	<0.02	0.01	0.002	<0.01	<0.01	18.17	1.33	0.003	0.08	0.42
635317	Drill Core	3.48	0.004	0.011	0.16	0.89	<2	0.008	<0.001	0.02	2.27	<0.02	<0.01	0.002	<0.01	<0.01	12.17	0.42	0.002	0.09	0.55
635318	Drill Core	3.50	0.002	0.007	0.05	0.57	<2	0.005	<0.001	0.02	1.09	<0.02	<0.01	0.001	<0.01	<0.01	14.03	0.10	0.001	0.06	0.32
635319	Drill Core	2.76	0.007	0.007	0.38	2.67	<2	0.013	<0.001	0.01	2.05	<0.02	<0.01	0.006	<0.01	<0.01	3.73	0.34	0.004	0.12	1.16
635320	Rock	0.38	<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	0.02	0.17	<0.02	0.01	<0.001	<0.01	<0.01	20.33	0.02	<0.001	10.69	0.13
635321	Drill Core	2.21	0.006	0.009	0.16	0.97	<2	0.011	<0.001	0.01	0.84	<0.02	<0.01	0.001	<0.01	<0.01	10.48	0.27	0.003	0.09	0.78
635322	Drill Core	1.65	0.010	0.018	0.25	1.43	2	0.017	<0.001	0.01	2.11	<0.02	<0.01	0.003	<0.01	<0.01	5.99	0.32	0.005	0.16	1.45
635323	Drill Core	3.25	0.012	0.013	0.06	0.85	<2	0.019	<0.001	<0.01	1.21	<0.02	<0.01	0.003	<0.01	<0.01	1.36	0.17	0.006	0.15	1.50
635324	Drill Core	2.62	0.005	0.013	0.12	0.27	<2	0.024	<0.001	<0.01	1.52	<0.02	<0.01	0.001	<0.01	<0.01	5.52	1.78	0.011	0.18	1.86
635325	Drill Core	0.49	0.001	0.010	0.55	0.03	3	0.019	<0.001	0.01	2.34	<0.02	0.01	<0.001	<0.01	<0.01	10.78	2.79	0.013	0.22	2.30
635326	Drill Core	3.42	<0.001	0.004	<0.02	<0.01	<2	0.004	<0.001	0.03	2.30	<0.02	0.01	<0.001	<0.01	<0.01	21.02	0.15	0.003	0.31	2.36
635327	Drill Core	1.68	0.007	0.027	0.11	0.60	2	0.018	<0.001	<0.01	4.15	<0.02	<0.01	<0.001	<0.01	<0.01	3.57	0.60	0.007	0.18	1.54
635328	Drill Core	1.58	<0.001	0.003	<0.02	<0.01	<2	0.004	<0.001	0.04	2.37	<0.02	0.02	<0.001	<0.01	<0.01	22.48	0.02	0.003	0.36	2.49
635329	Drill Core	1.83	0.004	0.009	0.08	0.20	<2	0.017	<0.001	0.01	3.51	<0.02	0.02	<0.001	<0.01	<0.01	14.47	3.85	0.009	0.19	1.66
635330	Rock Pulp	0.06	<0.001	0.469	1.37	2.79	18	<0.001	<0.001	0.42	2.54	<0.02	0.02	0.018	<0.01	<0.01	4.74	0.01	<0.001	0.32	4.20



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: December 23, 2010

Page: 2 of 5 **Part** 2

CERTIFICATE OF ANALYSIS

WHI10000669.1

	Method Analyte Unit MDL	7TD	7TD	7TD	7TD	G8SG	7TD.1
		Na	K	W	S	SG	Pb
		%	%	%	%		%
		0.01	0.01	0.01	0.05	0	0.02
635301	Drill Core	<0.01	0.60	<0.01	0.82	2.29	
635302	Drill Core	<0.01	0.91	<0.01	1.25	2.19	
635303	Drill Core	<0.01	0.79	<0.01	11.26	2.53	
635304	Drill Core	<0.01	0.39	<0.01	6.04	2.53	
635305	Drill Core	<0.01	0.67	<0.01	8.57	2.29	
635306	Drill Core	<0.01	0.10	<0.01	2.41	2.49	
635307	Drill Core	<0.01	0.32	<0.01	5.88	2.49	
635308	Drill Core	<0.01	0.12	<0.01	2.03	2.50	
635309	Drill Core	<0.01	0.52	<0.01	8.35	2.44	
635310	Drill Core	<0.01	0.12	<0.01	14.58	2.90	
635311	Drill Core	<0.01	0.11	<0.01	12.35	2.80	
635312	Drill Core	<0.01	0.12	<0.01	11.51	2.76	
635313	Drill Core	<0.01	0.32	<0.01	6.06	2.41	
635314	Drill Core	<0.01	0.43	<0.01	4.40	2.28	
635315	Drill Core	<0.01	0.04	<0.01	0.60	2.47	
635316	Drill Core	<0.01	0.22	<0.01	1.82	2.45	
635317	Drill Core	<0.01	0.30	<0.01	3.17	2.36	
635318	Drill Core	<0.01	0.17	<0.01	1.57	2.39	
635319	Drill Core	<0.01	0.62	<0.01	3.72	2.24	
635320	Rock	<0.01	0.10	<0.01	<0.05	2.53	
635321	Drill Core	<0.01	0.43	<0.01	1.41	2.28	
635322	Drill Core	<0.01	0.76	<0.01	3.20	2.31	
635323	Drill Core	<0.01	0.80	<0.01	1.69	2.23	
635324	Drill Core	<0.01	1.08	<0.01	1.88	2.20	
635325	Drill Core	<0.01	1.46	<0.01	2.77	2.40	
635326	Drill Core	<0.01	1.24	<0.01	2.66	2.63	
635327	Drill Core	<0.01	0.84	<0.01	5.31	2.35	
635328	Drill Core	<0.01	1.31	<0.01	2.74	2.60	
635329	Drill Core	<0.01	0.99	<0.01	4.18	2.43	
635330	Rock Pulp	1.67	1.21	<0.01	3.36	N.A.	



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: December 23, 2010

Page: 3 of 5 Part 1

CERTIFICATE OF ANALYSIS

WHI10000669.1

	Method Analyte Unit MDL	WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD
		Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg	Al
		kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%	%
		0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01	0.01
635331	Drill Core	1.78	0.007	0.007	0.13	0.97	<2	0.014	<0.001	<0.01	1.09	<0.02	<0.01	0.002	<0.01	<0.01	4.56	0.67	0.006	0.14	1.25
635332	Drill Core	0.45	<0.001	<0.001	0.07	0.32	<2	0.002	<0.001	0.02	0.47	<0.02	<0.01	<0.001	<0.01	<0.01	12.91	0.03	<0.001	0.05	0.24
635333	Drill Core	0.84	<0.001	0.001	1.02	3.26	<2	0.002	<0.001	0.04	0.89	<0.02	<0.01	0.017	<0.01	<0.01	14.17	0.05	<0.001	0.09	0.27
635334	Drill Core	2.79	0.004	0.008	<0.02	0.01	<2	0.009	<0.001	0.01	2.73	<0.02	<0.01	<0.001	<0.01	<0.01	2.86	0.13	0.003	0.21	1.78
635335	Drill Core	1.95	<0.001	0.002	<0.02	<0.01	<2	0.001	<0.001	0.07	1.06	<0.02	0.02	<0.001	<0.01	<0.01	28.83	0.10	<0.001	0.12	0.12
635336	Drill Core	2.75	0.002	0.004	<0.02	<0.01	<2	0.006	<0.001	<0.01	0.88	<0.02	<0.01	<0.001	<0.01	<0.01	2.60	0.11	0.002	0.15	1.20
635337	Drill Core	1.49	<0.001	0.003	<0.02	<0.01	<2	0.002	<0.001	0.06	1.59	<0.02	0.01	<0.001	<0.01	<0.01	23.82	0.05	<0.001	0.11	0.28
635338	Drill Core	2.98	0.001	0.005	0.12	0.37	<2	0.007	<0.001	0.02	1.56	<0.02	<0.01	<0.001	<0.01	<0.01	6.52	0.35	0.002	0.14	1.10
635339	Drill Core	1.31	<0.001	<0.001	<0.02	0.58	<2	0.002	<0.001	0.09	0.47	<0.02	0.01	0.003	<0.01	<0.01	24.12	<0.01	<0.001	0.14	0.19
635340	Drill Core	0.78	0.003	0.004	0.57	0.11	<2	0.010	<0.001	0.01	1.58	<0.02	<0.01	<0.001	<0.01	<0.01	3.44	0.48	0.004	0.16	1.66
635341	Drill Core	0.84	0.003	0.003	0.34	0.05	<2	0.010	<0.001	0.01	1.28	<0.02	<0.01	<0.001	<0.01	<0.01	4.14	0.41	0.004	0.17	1.78
635342	Drill Core	1.49	0.003	0.002	0.13	0.81	<2	0.007	<0.001	<0.01	0.81	<0.02	<0.01	0.003	<0.01	<0.01	0.55	0.02	0.002	0.10	1.03
635343	Drill Core	1.96	0.006	0.010	1.28	5.74	2	0.012	<0.001	0.01	5.52	<0.02	<0.01	0.024	<0.01	<0.01	0.64	0.04	0.002	0.14	1.68
635344	Drill Core	1.89	0.004	0.010	2.05	8.23	4	0.012	<0.001	0.02	5.68	<0.02	<0.01	0.034	<0.01	<0.01	3.79	0.08	0.003	0.14	1.46
635345	Drill Core	1.86	0.002	0.007	1.98	12.22	3	0.004	<0.001	0.02	6.18	<0.02	<0.01	0.049	<0.01	<0.01	1.95	0.02	0.001	0.06	0.56
635346	Drill Core	1.18	<0.001	0.003	>10	14.42	4	0.001	<0.001	0.01	2.18	<0.02	<0.01	0.090	<0.01	<0.01	2.86	<0.01	<0.001	0.03	0.19
635347	Drill Core	0.98	<0.001	0.003	>10	20.36	5	<0.001	<0.001	<0.01	1.59	<0.02	<0.01	0.163	<0.01	<0.01	0.74	<0.01	<0.001	0.02	0.15
635348	Drill Core	1.45	<0.001	0.006	>10	30.02	9	<0.001	<0.001	<0.01	0.98	<0.02	<0.01	0.255	<0.01	<0.01	0.07	<0.01	<0.001	0.01	0.11
635349	Drill Core	0.98	<0.001	0.004	>10	32.45	7	<0.001	<0.001	<0.01	0.62	<0.02	<0.01	0.274	<0.01	<0.01	0.42	<0.01	<0.001	<0.01	0.08
635350	Rock	0.41	<0.001	<0.001	0.05	0.12	<2	<0.001	<0.001	0.02	0.31	<0.02	0.01	<0.001	<0.01	<0.01	20.67	0.03	<0.001	10.88	0.27
635351	Drill Core	0.72	<0.001	0.004	>10	30.76	6	<0.001	<0.001	<0.01	1.53	<0.02	<0.01	0.260	<0.01	<0.01	0.12	<0.01	<0.001	0.02	0.09
635352	Drill Core	1.04	<0.001	0.003	>10	15.70	5	<0.001	<0.001	<0.01	7.14	<0.02	<0.01	0.130	<0.01	<0.01	0.95	<0.01	<0.001	0.02	0.11
635353	Drill Core	1.25	<0.001	0.003	8.89	18.27	5	<0.001	<0.001	<0.01	4.79	<0.02	<0.01	0.140	<0.01	<0.01	1.22	<0.01	<0.001	0.01	0.11
635354	Drill Core	3.98	0.003	0.005	1.51	4.92	<2	0.007	<0.001	0.02	4.52	<0.02	<0.01	0.015	<0.01	<0.01	4.34	0.04	0.001	0.08	0.77
635355	Drill Core	0.99	0.003	0.008	7.63	18.30	5	0.007	<0.001	0.02	5.46	<0.02	<0.01	0.073	<0.01	<0.01	1.97	0.08	0.002	0.09	1.22
635356	Drill Core	1.14	0.002	0.003	0.66	1.42	<2	0.006	<0.001	0.02	2.99	<0.02	<0.01	0.005	<0.01	<0.01	10.67	0.06	0.002	0.09	0.68
635357	Drill Core	2.31	0.001	0.002	0.37	1.41	<2	0.004	<0.001	0.01	0.90	<0.02	<0.01	0.005	<0.01	<0.01	4.18	0.03	<0.001	0.05	0.41
635358	Drill Core	2.23	0.002	0.007	0.55	1.48	<2	0.007	<0.001	0.01	2.34	<0.02	<0.01	0.005	<0.01	<0.01	4.06	0.06	0.001	0.08	0.78
635359	Drill Core	1.88	0.006	0.005	0.43	2.36	<2	0.011	<0.001	<0.01	1.42	<0.02	<0.01	0.008	<0.01	<0.01	0.89	0.05	0.003	0.12	1.58
635360	Rock Pulp	0.06	<0.001	0.674	5.96	6.65	70	<0.001	<0.001	0.09	4.91	<0.02	0.02	0.019	0.04	<0.01	1.39	0.02	<0.001	0.25	5.24



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: December 23, 2010

Page: 3 of 5 **Part** 2

CERTIFICATE OF ANALYSIS

WHI10000669.1

	Method Analyte Unit MDL	7TD	7TD	7TD	7TD	G8SG	7TD.1
		Na	K	W	S	SG	Pb
		%	%	%	%		%
		0.01	0.01	0.01	0.05	0	0.02
635331	Drill Core	<0.01	0.71	<0.01	1.69	2.27	
635332	Drill Core	<0.01	0.13	<0.01	0.56	2.49	
635333	Drill Core	<0.01	0.20	<0.01	2.87	2.61	
635334	Drill Core	<0.01	0.99	<0.01	2.96	2.38	
635335	Drill Core	<0.01	0.09	<0.01	1.27	2.51	
635336	Drill Core	<0.01	0.69	<0.01	0.73	2.36	
635337	Drill Core	<0.01	0.16	<0.01	1.90	2.52	
635338	Drill Core	<0.01	0.64	<0.01	1.72	2.42	
635339	Drill Core	0.01	0.11	<0.01	0.80	2.54	
635340	Drill Core	<0.01	0.98	<0.01	1.75	2.30	
635341	Drill Core	<0.01	1.06	<0.01	1.30	2.27	
635342	Drill Core	<0.01	0.60	<0.01	1.08	2.28	
635343	Drill Core	<0.01	1.05	<0.01	9.66	2.44	
635344	Drill Core	<0.01	0.85	<0.01	11.25	2.46	
635345	Drill Core	<0.01	0.34	<0.01	14.23	2.79	
635346	Drill Core	<0.01	0.10	<0.01	11.53	3.06	11.93
635347	Drill Core	<0.01	0.08	<0.01	13.87	3.11	11.66
635348	Drill Core	<0.01	0.05	<0.01	19.25	3.30	12.38
635349	Drill Core	<0.01	0.04	<0.01	19.45	3.37	12.01
635350	Rock	0.03	0.06	<0.01	0.10	2.61	
635351	Drill Core	<0.01	0.05	<0.01	19.60	3.34	12.03
635352	Drill Core	<0.01	0.06	<0.01	18.34	3.28	11.53
635353	Drill Core	<0.01	0.06	<0.01	16.48	3.07	
635354	Drill Core	<0.01	0.47	<0.01	7.64	2.53	
635355	Drill Core	<0.01	0.81	<0.01	16.61	2.85	
635356	Drill Core	<0.01	0.40	<0.01	4.16	2.43	
635357	Drill Core	<0.01	0.22	<0.01	1.44	2.42	
635358	Drill Core	<0.01	0.44	<0.01	3.22	2.36	
635359	Drill Core	<0.01	1.01	<0.01	2.60	2.28	
635360	Rock Pulp	2.29	1.30	<0.01	5.85	N.A.	



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: December 23, 2010

Page: 4 of 5 Part 1

CERTIFICATE OF ANALYSIS

WHI10000669.1

	Method Analyte Unit MDL	WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD
		Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg	Al
		kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%	%
		0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01	0.01
635361	Drill Core	1.76	0.005	0.003	0.33	0.08	<2	0.008	<0.001	0.01	1.65	<0.02	<0.01	<0.001	<0.01	<0.01	2.65	0.02	0.002	0.09	1.23
635362	Drill Core	1.84	0.002	0.008	4.06	9.64	2	0.005	<0.001	0.03	3.87	<0.02	<0.01	0.032	<0.01	<0.01	8.30	0.05	<0.001	0.07	0.51
635363	Drill Core	1.75	<0.001	<0.001	0.13	0.51	<2	<0.001	<0.001	0.07	0.31	<0.02	0.03	0.002	<0.01	<0.01	33.36	0.01	<0.001	0.10	0.03
635364	Drill Core	2.60	<0.001	0.003	1.49	4.46	<2	0.004	<0.001	0.03	2.20	<0.02	0.01	0.013	<0.01	<0.01	15.52	0.08	0.001	0.10	0.64
635365	Drill Core	1.61	<0.001	0.002	0.94	2.09	5	0.005	<0.001	0.03	1.78	<0.02	0.01	0.005	<0.01	<0.01	16.78	0.05	0.001	0.12	0.71
635366	Drill Core	1.06	<0.001	0.003	4.38	16.91	<2	<0.001	<0.001	0.03	1.48	<0.02	<0.01	0.067	<0.01	<0.01	15.94	0.03	<0.001	0.04	0.15
635367	Drill Core	1.18	<0.001	0.003	1.40	26.00	3	<0.001	<0.001	0.03	1.08	<0.02	<0.01	0.077	<0.01	<0.01	13.15	0.03	<0.001	0.04	0.13
635368	Drill Core	1.09	<0.001	0.001	0.73	2.54	2	0.002	<0.001	0.04	1.50	<0.02	0.02	0.007	<0.01	<0.01	29.05	0.02	<0.001	0.07	0.19
635369	Drill Core	1.70	0.001	0.003	1.75	6.32	<2	0.005	<0.001	0.03	5.42	<0.02	<0.01	0.019	<0.01	<0.01	9.60	0.06	0.001	0.08	0.52
635370	Drill Core	0.90	<0.001	0.002	0.53	1.15	<2	0.004	<0.001	0.02	1.30	<0.02	<0.01	0.003	<0.01	<0.01	8.92	0.04	<0.001	0.07	0.53
635371	Drill Core	0.98	0.001	0.002	0.27	1.30	<2	0.005	<0.001	0.02	1.38	<0.02	<0.01	0.003	<0.01	<0.01	10.94	0.04	<0.001	0.08	0.59
635372	Drill Core	1.63	0.002	0.012	6.86	39.48	10	0.007	<0.001	0.02	4.62	<0.02	<0.01	0.092	<0.01	<0.01	0.28	0.06	<0.001	0.06	0.51
635373	Drill Core	1.76	0.002	0.006	4.63	16.73	4	0.006	<0.001	0.02	4.38	<0.02	<0.01	0.041	<0.01	<0.01	1.61	0.05	<0.001	0.05	0.41
635374	Drill Core	1.26	<0.001	0.002	1.02	1.99	<2	0.003	<0.001	0.02	1.16	<0.02	<0.01	0.005	<0.01	<0.01	7.34	0.03	<0.001	0.05	0.37
635375	Drill Core	0.87	<0.001	0.003	0.53	3.25	<2	0.004	<0.001	0.03	0.98	<0.02	<0.01	0.008	<0.01	<0.01	12.02	0.04	<0.001	0.07	0.40
635376	Drill Core	2.01	<0.001	<0.001	0.12	0.33	<2	0.004	<0.001	0.03	0.55	<0.02	0.01	<0.001	<0.01	<0.01	19.59	0.04	<0.001	0.10	0.63
635377	Drill Core	2.12	<0.001	<0.001	0.03	0.13	<2	0.001	<0.001	0.05	0.18	<0.02	0.03	<0.001	<0.01	<0.01	32.10	0.02	<0.001	0.08	0.18
635378	Drill Core	2.91	0.001	0.003	0.06	0.03	<2	0.005	<0.001	0.03	0.94	<0.02	0.01	<0.001	<0.01	<0.01	20.78	0.05	0.001	0.12	0.78
635379	Drill Core	1.26	0.002	0.003	0.10	0.07	<2	0.007	<0.001	0.01	1.06	<0.02	<0.01	<0.001	<0.01	<0.01	2.52	0.04	0.001	0.10	0.84
635380	Rock	0.41	<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	0.01	0.13	<0.02	0.01	<0.001	<0.01	<0.01	21.60	0.03	<0.001	10.64	0.12
635381	Drill Core	2.71	<0.001	0.004	0.31	1.66	<2	0.004	<0.001	0.02	1.40	<0.02	<0.01	0.004	<0.01	<0.01	9.20	0.08	<0.001	0.07	0.35
635382	Drill Core	3.28	0.002	0.006	0.12	0.54	<2	0.005	<0.001	0.04	0.83	<0.02	0.01	0.001	<0.01	<0.01	21.23	0.43	0.001	0.11	0.41
635383	Drill Core	2.49	0.004	0.005	0.21	0.83	3	0.009	<0.001	0.02	0.82	<0.02	<0.01	0.002	<0.01	<0.01	8.14	0.32	0.003	0.10	0.75
635384	Drill Core	3.63	0.009	0.014	0.15	1.33	4	0.016	<0.001	<0.01	2.24	<0.02	<0.01	0.004	<0.01	<0.01	2.82	0.22	0.004	0.15	1.29
635385	Drill Core	3.45	0.004	0.013	0.24	0.31	5	0.027	<0.001	<0.01	2.06	<0.02	<0.01	<0.001	<0.01	<0.01	8.54	2.03	0.013	0.21	1.86
635386	Drill Core	2.96	<0.001	0.003	<0.02	<0.01	2	0.022	<0.001	0.03	2.11	<0.02	0.02	<0.001	<0.01	<0.01	17.96	0.08	0.003	0.32	2.34
635387	Drill Core	1.55	<0.001	<0.001	<0.02	<0.01	<2	0.009	<0.001	0.04	0.50	<0.02	0.03	<0.001	<0.01	<0.01	31.12	0.02	<0.001	0.19	0.76
635388	Drill Core	1.62	0.003	0.003	<0.02	<0.01	<2	0.040	<0.001	0.03	1.60	<0.02	0.02	<0.001	<0.01	<0.01	16.63	0.15	0.003	0.22	1.53
635389	Drill Core	1.85	0.010	0.009	<0.02	<0.01	4	0.026	0.001	0.01	2.95	<0.02	0.02	<0.001	<0.01	<0.01	11.72	3.72	0.012	0.33	3.29
635390	Rock Pulp	0.06	<0.001	0.479	1.40	2.97	20	<0.001	<0.001	0.45	2.67	<0.02	0.02	0.018	<0.01	<0.01	4.85	0.01	<0.001	0.33	4.15



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: December 23, 2010

Page: 4 of 5 **Part** 2

CERTIFICATE OF ANALYSIS

WHI10000669.1

	Method Analyte Unit MDL	7TD	7TD	7TD	7TD	G8SG	7TD.1
		Na	K	W	S	SG	Pb
		%	%	%	%		%
		0.01	0.01	0.01	0.05	0	0.02
635361	Drill Core	<0.01	0.87	<0.01	1.68	2.28	
635362	Drill Core	<0.01	0.32	<0.01	9.87	2.62	
635363	Drill Core	<0.01	0.02	<0.01	0.60	2.57	
635364	Drill Core	<0.01	0.40	<0.01	5.23	2.44	
635365	Drill Core	<0.01	0.45	<0.01	3.14	2.47	
635366	Drill Core	<0.01	0.08	<0.01	10.74	2.84	
635367	Drill Core	<0.01	0.07	<0.01	14.35	2.88	
635368	Drill Core	<0.01	0.10	<0.01	3.19	2.56	
635369	Drill Core	<0.01	0.32	<0.01	9.76	2.58	
635370	Drill Core	<0.01	0.34	<0.01	1.98	2.42	
635371	Drill Core	<0.01	0.39	<0.01	2.02	2.42	
635372	Drill Core	<0.01	0.29	<0.01	25.90	3.25	
635373	Drill Core	<0.01	0.23	<0.01	13.74	2.79	
635374	Drill Core	<0.01	0.24	<0.01	2.31	2.45	
635375	Drill Core	<0.01	0.27	<0.01	2.61	2.49	
635376	Drill Core	<0.01	0.36	<0.01	0.68	2.42	
635377	Drill Core	<0.01	0.10	<0.01	0.22	2.49	
635378	Drill Core	<0.01	0.44	<0.01	1.03	2.38	
635379	Drill Core	<0.01	0.51	<0.01	0.91	2.39	
635380	Rock	<0.01	0.03	<0.01	<0.05	2.60	
635381	Drill Core	<0.01	0.22	<0.01	2.25	2.46	
635382	Drill Core	<0.01	0.22	<0.01	1.18	2.39	
635383	Drill Core	<0.01	0.43	<0.01	1.12	2.31	
635384	Drill Core	<0.01	0.76	<0.01	3.08	2.19	
635385	Drill Core	<0.01	1.19	<0.01	2.39	2.04	
635386	Drill Core	<0.01	1.32	<0.01	2.36	2.20	
635387	Drill Core	<0.01	0.42	<0.01	0.51	2.38	
635388	Drill Core	<0.01	1.02	<0.01	1.81	1.98	
635389	Drill Core	<0.01	2.39	<0.01	3.21	2.05	
635390	Rock Pulp	1.75	1.24	<0.01	3.20	N.A.	



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: December 23, 2010

Page: 5 of 5 **Part** 1

CERTIFICATE OF ANALYSIS

WHI10000669.1

	Method Analyte Unit MDL	WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD
		Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg	Al
		kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%	%
		0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01	0.01
635391	Drill Core	2.51	0.008	0.015	0.04	0.86	5	0.032	0.001	<0.01	4.42	<0.02	<0.01	0.005	<0.01	<0.01	1.93	0.25	0.016	0.43	4.11



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**

Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: December 23, 2010

Page: 5 of 5 **Part** 2

CERTIFICATE OF ANALYSIS

WHI10000669.1

	Method	7TD	7TD	7TD	7TD	G8SG	7TD.1
	Analyte	Na	K	W	S	SG	Pb
	Unit	%	%	%	%		%
	MDL	0.01	0.01	0.01	0.05	0	0.02
635391	Drill Core	<0.01	2.94	<0.01	5.11	1.97	



Acme Analytical Laboratories (Vancouver) Ltd.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: **Selwyn Resources Ltd.**

Suite 700 - 509 Richards Street

Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: December 23, 2010

Page: 1 of 2 Part 1

QUALITY CONTROL REPORT

WHI10000669.1

	Method Analyte Unit MDL	WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	
		Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg	Al
		kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%	%
		0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01	0.01
Pulp Duplicates																					
635318	Drill Core	3.50	0.002	0.007	0.05	0.57	<2	0.005	<0.001	0.02	1.09	<0.02	<0.01	0.001	<0.01	<0.01	14.03	0.10	0.001	0.06	0.32
REP 635318	QC		0.002	0.007	0.05	0.58	<2	0.005	<0.001	0.02	1.09	<0.02	<0.01	0.001	<0.01	<0.01	14.75	0.10	0.001	0.06	0.32
635349	Drill Core	0.98	<0.001	0.004	>10	32.45	7	<0.001	<0.001	<0.01	0.62	<0.02	<0.01	0.274	<0.01	<0.01	0.42	<0.01	<0.001	<0.01	0.08
REP 635349	QC																				
635363	Drill Core	1.75	<0.001	<0.001	0.13	0.51	<2	<0.001	<0.001	0.07	0.31	<0.02	0.03	0.002	<0.01	<0.01	33.36	0.01	<0.001	0.10	0.03
REP 635363	QC		<0.001	<0.001	0.12	0.52	<2	<0.001	<0.001	0.07	0.31	<0.02	0.03	0.001	<0.01	<0.01	31.78	0.01	<0.001	0.10	0.03
635376	Drill Core	2.01	<0.001	<0.001	0.12	0.33	<2	0.004	<0.001	0.03	0.55	<0.02	0.01	<0.001	<0.01	<0.01	19.59	0.04	<0.001	0.10	0.63
REP 635376	QC		<0.001	<0.001	0.12	0.34	<2	0.004	<0.001	0.03	0.55	<0.02	0.01	<0.001	<0.01	<0.01	19.56	0.04	<0.001	0.10	0.63
Core Reject Duplicates																					
635309	Drill Core	2.04	0.002	0.004	1.35	4.43	2	0.007	<0.001	0.03	4.84	<0.02	0.01	0.010	<0.01	<0.01	12.00	0.07	0.002	0.12	0.92
DUP 635309	QC		0.002	0.005	1.41	4.52	2	0.007	<0.001	0.03	5.06	<0.02	<0.01	0.011	<0.01	<0.01	12.04	0.07	0.002	0.12	0.92
635344	Drill Core	1.89	0.004	0.010	2.05	8.23	4	0.012	<0.001	0.02	5.68	<0.02	<0.01	0.034	<0.01	<0.01	3.79	0.08	0.003	0.14	1.46
DUP 635344	QC		0.004	0.010	2.06	8.11	4	0.011	<0.001	0.02	5.75	<0.02	<0.01	0.034	<0.01	<0.01	3.96	0.07	0.003	0.14	1.43
635379	Drill Core	1.26	0.002	0.003	0.10	0.07	<2	0.007	<0.001	0.01	1.06	<0.02	<0.01	<0.001	<0.01	<0.01	2.52	0.04	0.001	0.10	0.84
DUP 635379	QC		0.002	0.003	0.11	0.08	<2	0.007	<0.001	0.01	1.14	<0.02	<0.01	<0.001	<0.01	<0.01	2.41	0.04	0.001	0.10	0.85
Reference Materials																					
STD CCU-1C	Standard																				
STD CZN-3	Standard																				
STD OREAS131A	Standard		<0.001	0.032	1.66	2.82	30	0.003	0.002	0.17	5.69	<0.02	<0.01	0.008	<0.01	<0.01	5.18	0.06	0.002	3.08	4.56
STD OREAS131A	Standard		<0.001	0.032	1.74	2.89	31	0.003	0.002	0.17	5.83	<0.02	<0.01	0.008	<0.01	<0.01	5.31	0.05	0.002	3.17	4.70
STD OREAS131A	Standard		<0.001	0.032	1.69	2.84	31	0.002	0.002	0.17	5.81	<0.02	<0.01	0.008	<0.01	<0.01	5.29	0.06	0.002	3.13	4.54
STD PTC-1A	Standard																				
STD R4T	Standard		0.064	0.509	1.56	3.39	85	0.354	0.040	0.09	24.03	<0.02	0.02	0.019	0.02	<0.01	2.22	0.04	0.018	1.43	4.00
STD R4T	Standard		0.064	0.515	1.54	3.44	91	0.353	0.040	0.09	23.93	<0.02	0.02	0.018	0.02	<0.01	2.20	0.05	0.018	1.43	3.97
STD R4T	Standard		0.064	0.510	1.59	3.43	88	0.356	0.042	0.09	24.07	<0.02	0.02	0.019	0.01	<0.01	2.19	0.05	0.019	1.43	3.98
STD SARM 71	Standard																				
STD SU-1B	Standard		<0.001	1.157	<0.02	0.03	6	1.969	0.065	0.07	24.70	<0.02	0.03	<0.001	<0.01	<0.01	2.17	0.06	0.028	1.77	4.34
STD SU-1B	Standard		<0.001	1.192	<0.02	0.03	7	1.992	0.067	0.07	25.03	<0.02	0.03	<0.001	<0.01	<0.01	2.26	0.06	0.031	1.81	4.44



Acme Analytical Laboratories (Vancouver) Ltd.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: Selwyn Resources Ltd.

Suite 700 - 509 Richards Street

Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: December 23, 2010

Page: 1 of 2 **Part** 2

QUALITY CONTROL REPORT

WHI10000669.1

Method		7TD	7TD	7TD	7TD	G8SG	7TD.1
Analyte		Na	K	W	S	SG	Pb
Unit		%	%	%	%		%
MDL		0.01	0.01	0.01	0.05	0	0.02
Pulp Duplicates							
635318	Drill Core	<0.01	0.17	<0.01	1.57	2.39	
REP 635318	QC	<0.01	0.17	<0.01	1.53		
635349	Drill Core	<0.01	0.04	<0.01	19.45	3.37	12.01
REP 635349	QC						12.25
635363	Drill Core	<0.01	0.02	<0.01	0.60	2.57	
REP 635363	QC	<0.01	0.02	<0.01	0.63		
635376	Drill Core	<0.01	0.36	<0.01	0.68	2.42	
REP 635376	QC	<0.01	0.36	<0.01	0.67		
Core Reject Duplicates							
635309	Drill Core	<0.01	0.52	<0.01	8.35	2.44	
DUP 635309	QC	<0.01	0.52	<0.01	9.08	2.49	
635344	Drill Core	<0.01	0.85	<0.01	11.25	2.46	
DUP 635344	QC	<0.01	0.83	<0.01	11.36	2.44	
635379	Drill Core	<0.01	0.51	<0.01	0.91	2.39	
DUP 635379	QC	0.01	0.52	<0.01	0.96	2.38	
Reference Materials							
STD CCU-1C	Standard						0.39
STD CZN-3	Standard						0.14
STD OREAS131A	Standard	0.15	3.29	<0.01	4.94		
STD OREAS131A	Standard	0.15	3.38	<0.01	4.98		
STD OREAS131A	Standard	0.15	3.41	<0.01	4.73		
STD PTC-1A	Standard						0.05
STD R4T	Standard	0.91	1.15	<0.01	13.19		
STD R4T	Standard	0.91	1.15	<0.01	13.26		
STD R4T	Standard	0.93	1.19	<0.01	12.21		
STD SARM 71	Standard						<0.02
STD SU-1B	Standard	1.64	0.60	<0.01	10.10		
STD SU-1B	Standard	1.73	0.61	<0.01	8.96		



Acme Analytical Laboratories (Vancouver) Ltd.
1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: December 23, 2010

Page: 2 of 2 Part 1

QUALITY CONTROL REPORT

WHI10000669.1

		WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	
		Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg	Al
		kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%	%
		0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01	0.01
STD SU-1B	Standard	<0.001	1.177	<0.02	0.03	7	1.980	0.068	0.07	25.17	<0.02	0.03	<0.001	<0.01	<0.01	2.23	0.06	0.031	1.81	4.39	
STD R4T Expected		0.062	0.502	1.518	3.376	86	0.339	0.039	0.086	24.07	0.0087	0.0185	0.018	0.0138	0.0018	2.166	0.045	0.018	1.384	3.897	
STD OREAS131A Expected		0.001	0.0322	1.72	2.83	30.9	0.0027	0.0023	0.1722	5.8166	0.0082	0.0028	0.0081	0.0047	0.001	5.286	0.0536	0.0025	3.1182	4.6057	
STD SU-1B Expected		0.0004	1.185	0.0058	0.0235	6.4	1.97	0.0672	0.0703	25.54	0.00025	0.03	0.0003	0.00002	0.0003	2.21	0.06	0.032	1.79	4.39	
STD CZN-3 Expected																					
STD CCU-1C Expected																					
STD PTC-1A Expected																					
BLK	Blank	<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	<0.01	<0.01	<0.02	<0.01	<0.001	<0.01	<0.01	<0.01	<0.01	<0.001	<0.01	<0.01	
BLK	Blank	<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	<0.01	<0.01	<0.02	<0.01	<0.001	<0.01	<0.01	<0.01	<0.01	<0.001	<0.01	<0.01	
BLK	Blank	<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	<0.01	<0.01	<0.02	<0.01	<0.001	<0.01	<0.01	<0.01	<0.01	<0.001	<0.01	<0.01	
BLK	Blank																				
Prep Wash																					
G1	Prep Blank	<0.001	<0.001	<0.02	0.01	<2	<0.001	<0.001	0.07	2.32	<0.02	0.08	<0.001	<0.01	<0.01	2.35	0.08	<0.001	0.60	7.78	
G1	Prep Blank	<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	0.07	2.41	<0.02	0.07	<0.001	<0.01	<0.01	2.38	0.08	<0.001	0.63	7.97	



Acme Analytical Laboratories (Vancouver) Ltd.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: **Selwyn Resources Ltd.**

Suite 700 - 509 Richards Street

Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: December 23, 2010

Page: 2 of 2 **Part** 2

QUALITY CONTROL REPORT

WHI10000669.1

		7TD Na %	7TD K %	7TD W %	7TD S %	G8SG SG 0	7TD.1 Pb %
		0.01	0.01	0.01	0.05	0	0.02
STD SU-1B	Standard	1.70	0.62	<0.01	8.28		
STD R4T Expected		0.9	1.153	0.00016	12.9903		
STD OREAS131A Expected		0.1501	3.1584	0.0005	4.8		
STD SU-1B Expected		1.662	0.6	0.0007	8.76		
STD CZN-3 Expected							0.113
STD CCU-1C Expected							0.34
STD PTC-1A Expected							0.05
BLK	Blank	<0.01	<0.01	<0.01	<0.05		
BLK	Blank	<0.01	<0.01	<0.01	<0.05		
BLK	Blank	<0.01	<0.01	<0.01	<0.05		
BLK	Blank						<0.02
Prep Wash							
G1	Prep Blank	2.89	2.99	<0.01	0.07	2.59	
G1	Prep Blank	2.81	3.00	<0.01	<0.05	2.64	



1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: Selwyn Resources Ltd.

Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Submitted By: Jason K. Dunning

Receiving Lab: Canada-Whitehorse

Received: November 29, 2010

Report Date: December 16, 2010

Page: 1 of 6

CERTIFICATE OF ANALYSIS

WHI10000668.1

CLIENT JOB INFORMATION

Project: Selwyn Project
Shipment ID:
P.O. Number: 1103
Number of Samples: 121

SAMPLE DISPOSAL

STOR-PLP Store After 90 days Invoice for Storage
STOR-RJT Store After 90 days Invoice for Storage

Acme does not accept responsibility for samples left at the laboratory after 90 days without prior written instructions for sample storage or return.

Invoice To: Selwyn Resources Ltd.
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6
Canada

CC:

SAMPLE PREPARATION AND ANALYTICAL PROCEDURES

Method Code	Number of Samples	Code Description	Test Wgt (g)	Report Status	Lab
R200-250	117	Crush split and pulverize 250g drill core to 200 mesh			WHI
7TD2	121	4 Acid digestion ICP-ES analysis.	0.5	Completed	VAN
G812	121	Specific Gravity on Pulp		Completed	VAN

ADDITIONAL COMMENTS



This report supersedes all previous preliminary and final reports with this file number dated prior to the date on this certificate. Signature indicates final approval; preliminary reports are unsigned and should be used for reference only.
All results are considered the confidential property of the client. Acme assumes the liabilities for actual cost of analysis only.
** asterisk indicates that an analytical result could not be provided due to unusually high levels of interference from other elements.



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: December 16, 2010

Page: 2 of 6 Part 1

CERTIFICATE OF ANALYSIS

WHI10000668.1

	Method Analyte Unit MDL	WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD
		Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg	Al
		kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%	%
		0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01	0.01
635151	Drill Core	1.21	<0.001	0.005	0.04	0.04	<2	0.013	<0.001	<0.01	1.52	<0.02	0.01	0.002	<0.01	<0.01	7.43	2.35	0.007	0.99	3.52
635152	Drill Core	1.35	<0.001	0.011	1.00	7.94	8	0.004	<0.001	0.02	3.61	<0.02	0.02	0.025	<0.01	<0.01	11.30	0.15	0.002	0.31	0.75
635153	Drill Core	1.58	0.001	0.006	0.04	0.13	<2	0.012	<0.001	0.01	1.70	<0.02	0.01	0.002	<0.01	<0.01	8.79	1.63	0.006	0.82	3.49
635154	Drill Core	0.70	0.001	0.003	0.03	0.16	<2	0.007	<0.001	0.01	0.84	<0.02	<0.01	0.002	<0.01	<0.01	5.48	1.15	0.003	0.18	1.59
635155	Drill Core	1.25	0.001	0.003	<0.02	0.05	<2	0.007	<0.001	0.02	0.74	<0.02	<0.01	0.002	<0.01	<0.01	7.11	0.51	0.002	0.12	1.07
635156	Drill Core	1.20	0.004	0.003	0.03	0.23	<2	0.008	<0.001	0.04	1.11	<0.02	0.01	0.002	<0.01	<0.01	15.19	0.07	0.002	0.16	1.29
635157	Drill Core	2.29	0.003	0.008	0.29	0.44	2	0.012	<0.001	0.02	9.47	<0.02	<0.01	0.003	<0.01	<0.01	5.42	0.05	0.002	0.10	0.93
635158	Drill Core	1.17	0.002	0.005	4.90	6.63	3	0.005	<0.001	0.02	5.02	<0.02	<0.01	0.024	<0.01	<0.01	11.49	0.04	0.001	0.08	0.53
635159	Drill Core	1.42	<0.001	0.006	0.43	14.12	<2	0.003	<0.001	<0.01	3.97	<0.02	<0.01	0.055	<0.01	<0.01	1.10	0.02	<0.001	0.03	0.23
635160	Drill Core	0.89	0.002	0.004	0.08	0.29	<2	0.007	<0.001	0.01	4.11	<0.02	<0.01	0.001	<0.01	<0.01	4.60	0.06	0.001	0.07	0.62
635161	Drill Core	0.75	0.002	0.003	0.08	0.85	<2	0.006	<0.001	0.01	4.20	<0.02	<0.01	0.003	<0.01	<0.01	5.06	0.06	0.001	0.07	0.57
635162	Drill Core	2.54	0.007	0.005	<0.02	0.01	<2	0.012	0.001	0.01	1.72	<0.02	<0.01	<0.001	<0.01	<0.01	7.54	0.04	0.002	0.14	1.40
635163	Drill Core	0.88	0.005	0.011	0.31	0.54	2	0.016	<0.001	0.04	8.98	<0.02	<0.01	0.002	<0.01	<0.01	6.66	0.07	0.001	0.09	0.86
635164	Drill Core	2.50	<0.001	<0.001	<0.02	0.01	<2	<0.001	<0.001	0.07	0.29	<0.02	0.02	<0.001	<0.01	<0.01	34.47	0.02	<0.001	0.13	0.10
635165	Drill Core	2.04	<0.001	<0.001	0.03	0.23	<2	0.001	<0.001	0.08	0.40	<0.02	0.02	0.001	<0.01	<0.01	33.28	0.04	<0.001	0.13	0.17
635166	Drill Core	1.56	<0.001	0.003	0.73	2.46	<2	0.003	<0.001	0.05	4.71	<0.02	0.01	0.011	<0.01	<0.01	21.64	0.06	0.001	0.09	0.38
635167	Drill Core	2.32	0.001	0.003	0.90	3.65	<2	0.006	<0.001	0.02	2.49	<0.02	<0.01	0.011	<0.01	<0.01	5.06	0.08	0.001	0.09	0.82
635168	Drill Core	1.62	0.002	0.003	0.51	2.53	<2	0.004	<0.001	0.05	2.11	<0.02	0.02	0.007	<0.01	<0.01	27.02	0.03	0.001	0.10	0.48
635169	Drill Core	0.94	0.001	0.002	0.64	2.08	<2	0.003	<0.001	0.05	1.19	<0.02	0.02	0.006	<0.01	<0.01	29.14	0.02	<0.001	0.08	0.34
635170	Rock	0.35	<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	0.02	0.14	<0.02	0.01	<0.001	<0.01	<0.01	20.46	0.03	<0.001	10.86	0.09
635171	Drill Core	1.31	0.001	0.001	0.81	1.82	<2	0.002	<0.001	0.05	0.96	<0.02	0.02	0.006	<0.01	<0.01	31.31	0.02	<0.001	0.10	0.29
635172	Drill Core	1.18	0.003	0.002	0.70	3.08	<2	0.005	<0.001	0.04	1.90	<0.02	0.02	0.012	<0.01	<0.01	27.06	0.05	0.001	0.13	0.73
635173	Drill Core	2.45	<0.001	0.003	8.39	21.59	6	0.002	<0.001	0.02	2.16	<0.02	<0.01	0.092	<0.01	<0.01	12.70	0.03	<0.001	0.04	0.17
635174	Drill Core	2.52	0.001	0.003	1.65	4.99	<2	0.005	<0.001	0.02	2.27	<0.02	<0.01	0.014	<0.01	<0.01	6.13	0.07	0.001	0.09	0.77
635175	Drill Core	1.20	0.002	0.004	0.76	5.06	<2	0.004	<0.001	0.04	3.03	<0.02	0.01	0.013	<0.01	<0.01	22.06	0.03	0.001	0.09	0.38
635176	Drill Core	2.49	0.002	0.004	0.71	4.05	<2	0.006	<0.001	0.02	1.92	<0.02	<0.01	0.011	<0.01	<0.01	6.04	0.06	0.001	0.08	0.86
635177	Drill Core	1.61	0.002	0.003	0.90	1.68	<2	0.005	<0.001	0.05	0.85	<0.02	0.01	0.005	<0.01	<0.01	22.28	0.05	0.002	0.13	0.73
635178	Drill Core	1.12	0.001	0.003	0.19	0.40	<2	0.007	<0.001	0.02	1.08	<0.02	<0.01	0.002	<0.01	<0.01	9.60	0.08	0.002	0.11	0.84
635179	Drill Core	1.34	<0.001	0.003	2.56	4.65	<2	0.002	<0.001	0.03	1.88	<0.02	0.01	0.024	<0.01	<0.01	19.98	0.03	<0.001	0.05	0.21
635180	Rock Pulp	0.06	0.001	0.660	6.06	6.68	69	0.001	<0.001	0.10	4.80	<0.02	0.02	0.018	0.04	<0.01	1.33	0.02	0.001	0.24	5.04



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: December 16, 2010

Page: 2 of 6 **Part** 2

CERTIFICATE OF ANALYSIS

WHI10000668.1

	Method	7TD	7TD	7TD	7TD	G8SG
Analyte	Na	K	W	S	SG	
Unit	%	%	%	%		
MDL	0.01	0.01	0.01	0.05	0	
635151	Drill Core	0.02	2.17	<0.01	1.57	2.17
635152	Drill Core	<0.01	0.49	<0.01	9.26	2.65
635153	Drill Core	0.01	1.89	<0.01	1.94	2.19
635154	Drill Core	<0.01	0.87	<0.01	0.93	2.38
635155	Drill Core	<0.01	0.60	<0.01	0.79	2.33
635156	Drill Core	<0.01	0.79	<0.01	1.42	2.32
635157	Drill Core	<0.01	0.53	<0.01	12.05	2.60
635158	Drill Core	<0.01	0.32	<0.01	11.21	2.77
635159	Drill Core	<0.01	0.12	*	12.70	2.80
635160	Drill Core	<0.01	0.34	<0.01	5.28	2.47
635161	Drill Core	<0.01	0.31	<0.01	5.46	2.51
635162	Drill Core	<0.01	0.80	<0.01	1.97	2.25
635163	Drill Core	<0.01	0.51	<0.01	12.09	2.57
635164	Drill Core	<0.01	0.06	<0.01	0.46	2.50
635165	Drill Core	<0.01	0.10	<0.01	0.62	2.46
635166	Drill Core	<0.01	0.21	<0.01	7.55	2.60
635167	Drill Core	<0.01	0.48	<0.01	5.07	2.42
635168	Drill Core	<0.01	0.26	<0.01	4.21	2.57
635169	Drill Core	<0.01	0.18	<0.01	2.73	2.48
635170	Rock	<0.01	0.03	<0.01	<0.05	2.54
635171	Drill Core	<0.01	0.16	<0.01	2.36	2.55
635172	Drill Core	<0.01	0.38	<0.01	4.22	2.55
635173	Drill Core	<0.01	0.09	<0.01	15.67	3.08
635174	Drill Core	<0.01	0.43	<0.01	5.63	2.52
635175	Drill Core	<0.01	0.21	<0.01	6.25	2.62
635176	Drill Core	0.23	0.45	<0.01	4.55	2.37
635177	Drill Core	<0.01	0.37	<0.01	1.76	2.43
635178	Drill Core	<0.01	0.46	<0.01	1.23	2.36
635179	Drill Core	<0.01	0.10	<0.01	4.61	2.64
635180	Rock Pulp	2.30	1.36	<0.01	5.84	N.A.



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: December 16, 2010

Page: 3 of 6 Part 1

CERTIFICATE OF ANALYSIS

WHI10000668.1

	Method Analyte Unit MDL	WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD
		Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg	Al
		kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%	%
		0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01	0.01
635181	Drill Core	1.31	0.002	0.009	0.32	0.01	<2	0.010	<0.001	0.02	6.00	<0.02	<0.01	<0.001	<0.01	<0.01	8.92	0.11	0.003	0.15	1.31
635182	Drill Core	2.44	0.001	0.003	0.10	0.07	<2	0.005	<0.001	0.04	1.38	<0.02	0.01	<0.001	<0.01	<0.01	23.35	0.06	0.002	0.13	0.83
635183	Drill Core	1.39	0.001	0.004	0.08	0.21	<2	0.005	<0.001	0.03	2.17	<0.02	0.01	<0.001	<0.01	<0.01	17.18	0.06	0.002	0.11	0.75
635184	Drill Core	1.20	<0.001	0.002	<0.02	0.12	<2	0.003	<0.001	0.04	1.40	<0.02	0.02	<0.001	<0.01	<0.01	32.73	0.03	<0.001	0.08	0.23
635185	Drill Core	1.64	0.001	0.004	0.02	0.01	<2	0.005	<0.001	0.04	1.78	<0.02	0.01	<0.001	<0.01	<0.01	24.16	0.06	0.001	0.12	0.64
635186	Drill Core	2.26	0.003	0.004	0.09	0.28	<2	0.009	<0.001	0.02	1.92	<0.02	<0.01	<0.001	<0.01	<0.01	9.57	0.06	0.002	0.13	1.20
635187	Drill Core	1.72	0.002	0.005	0.40	1.37	<2	0.011	<0.001	0.03	1.86	<0.02	<0.01	0.003	<0.01	<0.01	9.59	0.13	0.001	0.14	0.64
635188	Drill Core	2.51	0.002	0.007	0.09	1.20	<2	0.007	<0.001	0.04	0.78	<0.02	0.01	0.003	<0.01	<0.01	22.33	0.32	0.001	0.08	0.36
635189	Drill Core	3.09	0.002	0.007	0.05	0.19	<2	0.004	<0.001	0.04	0.64	<0.02	0.01	<0.001	<0.01	<0.01	23.27	0.47	0.001	0.07	0.13
635190	Drill Core	0.44	0.002	0.005	0.05	0.17	<2	0.004	<0.001	0.06	0.68	<0.02	0.02	<0.001	<0.01	<0.01	31.21	0.25	<0.001	0.08	0.10
635191	Drill Core	0.52	0.002	0.006	0.07	0.19	<2	0.005	<0.001	0.05	1.06	<0.02	0.02	<0.001	<0.01	<0.01	30.55	0.27	<0.001	0.08	0.11
635192	Drill Core	1.24	0.001	0.003	0.06	0.20	<2	0.003	<0.001	0.05	0.78	<0.02	0.01	<0.001	<0.01	<0.01	27.87	0.02	<0.001	0.07	0.14
635193	Drill Core	1.07	0.004	0.010	0.47	0.35	<2	0.007	<0.001	0.04	0.75	<0.02	0.02	<0.001	<0.01	<0.01	26.73	0.44	0.002	0.10	0.54
635194	Drill Core	1.37	0.005	0.016	0.26	1.91	2	0.012	<0.001	0.01	1.33	<0.02	<0.01	0.004	<0.01	<0.01	9.47	0.68	0.003	0.11	0.87
635195	Drill Core	1.44	0.002	0.005	0.05	0.35	<2	0.005	<0.001	0.03	1.50	<0.02	0.01	<0.001	<0.01	<0.01	15.94	0.18	0.001	0.07	0.33
635196	Drill Core	1.23	0.006	0.010	0.24	2.17	<2	0.014	<0.001	0.01	1.71	<0.02	<0.01	0.005	<0.01	<0.01	5.97	0.26	0.003	0.11	1.06
635197	Drill Core	2.08	0.008	0.015	0.14	1.47	<2	0.016	<0.001	0.01	1.48	<0.02	<0.01	0.004	<0.01	<0.01	6.87	0.33	0.004	0.13	1.13
635198	Drill Core	1.81	0.010	0.015	0.05	0.88	2	0.021	<0.001	<0.01	3.52	<0.02	<0.01	0.003	<0.01	<0.01	2.59	0.11	0.004	0.14	1.32
635199	Drill Core	0.97	0.007	0.012	0.07	0.71	<2	0.026	<0.001	<0.01	1.05	<0.02	<0.01	0.002	<0.01	<0.01	5.02	1.95	0.009	0.18	1.74
635200	Rock	0.39	<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	0.02	0.12	<0.02	<0.01	<0.001	<0.01	<0.01	21.39	0.03	<0.001	10.95	0.05
635201	Drill Core	1.54	<0.001	0.011	0.37	0.29	3	0.024	<0.001	<0.01	1.86	<0.02	0.01	<0.001	<0.01	<0.01	9.86	2.90	0.010	0.24	2.22
635202	Drill Core	2.69	<0.001	0.002	<0.02	<0.01	<2	0.002	<0.001	0.04	1.80	<0.02	0.02	<0.001	<0.01	<0.01	25.93	0.03	0.003	0.38	2.33
635203	Drill Core	1.46	0.001	0.002	<0.02	<0.01	<2	0.007	<0.001	0.04	1.89	<0.02	0.02	<0.001	<0.01	<0.01	22.46	1.16	0.003	0.32	2.42
635204	Drill Core	1.11	<0.001	0.002	<0.02	<0.01	<2	0.006	<0.001	0.03	1.65	<0.02	0.02	<0.001	<0.01	<0.01	23.93	0.02	0.002	0.26	1.33
635205	Drill Core	1.19	0.002	0.015	0.05	<0.01	<2	0.015	<0.001	0.03	6.40	<0.02	0.01	<0.001	<0.01	<0.01	16.72	0.06	0.005	0.31	2.43
635206	Drill Core	1.71	<0.001	0.002	<0.02	<0.01	<2	0.004	<0.001	0.02	0.57	<0.02	0.02	<0.001	<0.01	<0.01	21.41	0.56	0.001	0.13	0.61
635207	Drill Core	1.21	<0.001	0.006	<0.02	0.23	<2	0.011	<0.001	<0.01	0.89	<0.02	<0.01	<0.001	<0.01	<0.01	6.03	1.85	0.003	0.11	1.27
635208	Drill Core	1.50	<0.001	0.003	<0.02	0.19	<2	0.009	<0.001	<0.01	0.66	<0.02	<0.01	<0.001	<0.01	<0.01	5.27	1.56	0.002	0.10	1.07
635209	Drill Core	2.02	0.001	0.004	0.08	0.71	<2	0.008	<0.001	0.02	1.05	<0.02	<0.01	0.003	<0.01	<0.01	6.01	0.83	0.003	0.15	1.41
635210	Rock Pulp	0.06	<0.001	0.497	1.49	4.35	26	0.001	0.001	0.66	5.33	<0.02	0.01	0.028	<0.01	<0.01	4.32	0.05	0.003	1.55	4.61



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: December 16, 2010

Page: 3 of 6 **Part** 2

CERTIFICATE OF ANALYSIS

WHI10000668.1

	Method	7TD	7TD	7TD	7TD	G8SG
Analyte	Na	K	W	S	SG	
Unit	%	%	%	%		
MDL	0.01	0.01	0.01	0.05	0	
635181	Drill Core	<0.01	0.74	<0.01	7.42	2.44
635182	Drill Core	<0.01	0.44	<0.01	1.60	2.43
635183	Drill Core	<0.01	0.44	<0.01	2.70	2.37
635184	Drill Core	<0.01	0.15	<0.01	1.71	2.39
635185	Drill Core	<0.01	0.39	<0.01	2.12	2.34
635186	Drill Core	<0.01	0.71	<0.01	2.32	2.25
635187	Drill Core	<0.01	0.34	<0.01	2.74	2.27
635188	Drill Core	<0.01	0.22	<0.01	1.40	2.33
635189	Drill Core	<0.01	0.09	<0.01	0.78	2.36
635190	Drill Core	<0.01	0.08	<0.01	0.87	2.38
635191	Drill Core	<0.01	0.09	<0.01	1.34	2.35
635192	Drill Core	<0.01	0.10	<0.01	1.01	2.40
635193	Drill Core	<0.01	0.32	<0.01	1.05	2.28
635194	Drill Core	<0.01	0.49	<0.01	2.42	2.13
635195	Drill Core	<0.01	0.19	<0.01	1.85	2.37
635196	Drill Core	<0.01	0.59	<0.01	2.99	2.15
635197	Drill Core	<0.01	0.64	<0.01	2.33	2.11
635198	Drill Core	<0.01	0.75	<0.01	4.47	2.09
635199	Drill Core	<0.01	0.99	<0.01	1.39	1.87
635200	Rock	<0.01	0.02	<0.01	<0.05	2.58
635201	Drill Core	<0.01	1.21	<0.01	2.27	1.95
635202	Drill Core	<0.01	1.10	<0.01	2.04	2.51
635203	Drill Core	<0.01	1.20	<0.01	2.04	2.44
635204	Drill Core	<0.01	0.82	<0.01	1.78	2.40
635205	Drill Core	<0.01	1.33	<0.01	7.62	2.47
635206	Drill Core	<0.01	0.42	<0.01	0.45	2.40
635207	Drill Core	<0.01	0.86	<0.01	0.90	2.26
635208	Drill Core	<0.01	0.68	<0.01	0.65	2.30
635209	Drill Core	0.12	0.84	<0.01	1.31	2.28
635210	Rock Pulp	0.10	3.28	<0.01	5.20	N.A.



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: December 16, 2010

Page: 4 of 6 Part 1

CERTIFICATE OF ANALYSIS

WHI10000668.1

	Method Analyte Unit MDL	WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD
		Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg	Al
		kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%	%
		0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01	0.01
635211	Drill Core	1.10	0.004	0.004	0.12	0.75	<2	0.010	<0.001	<0.01	1.06	<0.02	<0.01	0.004	<0.01	<0.01	0.22	0.05	0.002	0.15	1.51
635212	Drill Core	0.92	0.003	0.011	2.91	6.65	<2	0.007	<0.001	0.01	5.01	<0.02	<0.01	0.044	<0.01	<0.01	0.98	0.04	0.002	0.09	1.02
635213	Drill Core	1.35	0.003	0.011	2.16	9.62	3	0.010	<0.001	0.01	7.75	<0.02	<0.01	0.039	<0.01	<0.01	1.64	0.05	0.002	0.10	1.25
635214	Drill Core	1.60	<0.001	0.006	2.08	20.15	<2	0.002	<0.001	0.01	6.32	<0.02	<0.01	0.092	<0.01	<0.01	3.48	0.01	<0.001	0.02	0.16
635215	Drill Core	1.72	<0.001	0.006	3.55	25.16	<2	0.003	<0.001	<0.01	2.51	<0.02	<0.01	0.118	<0.01	<0.01	0.46	0.03	<0.001	0.03	0.35
635216	Drill Core	0.92	0.002	0.004	3.08	4.83	<2	0.006	<0.001	0.03	4.33	<0.02	<0.01	0.019	<0.01	<0.01	9.31	0.03	0.001	0.09	0.47
635217	Drill Core	1.42	0.002	0.002	0.29	2.39	<2	0.004	<0.001	0.05	2.22	<0.02	0.01	0.007	<0.01	<0.01	25.44	0.03	<0.001	0.16	0.42
635218	Drill Core	1.36	0.003	0.004	1.13	5.50	<2	0.005	<0.001	0.02	3.66	<0.02	<0.01	0.015	<0.01	<0.01	7.43	0.05	0.001	0.07	0.66
635219	Drill Core	1.29	0.002	0.003	1.20	2.71	2	0.005	<0.001	0.06	0.94	<0.02	0.01	0.007	<0.01	<0.01	20.43	0.05	0.001	0.11	0.53
635220	Drill Core	0.91	0.002	0.002	0.57	0.85	<2	0.005	<0.001	0.02	0.83	<0.02	<0.01	0.002	<0.01	<0.01	10.25	0.07	<0.001	0.08	0.67
635221	Drill Core	0.81	0.002	0.002	0.26	0.81	<2	0.005	<0.001	0.02	0.81	<0.02	<0.01	0.002	<0.01	<0.01	8.80	0.09	0.001	0.07	0.64
635222	Drill Core	1.90	0.004	0.003	0.08	0.77	<2	0.009	<0.001	<0.01	1.50	<0.02	<0.01	0.002	<0.01	<0.01	0.73	0.06	0.002	0.09	1.01
635223	Drill Core	1.34	0.008	0.005	0.18	0.97	2	0.013	<0.001	<0.01	2.64	<0.02	<0.01	0.003	<0.01	<0.01	1.47	0.06	0.003	0.13	1.75
635224	Drill Core	1.25	0.004	0.011	0.85	5.35	<2	0.008	<0.001	0.03	13.16	<0.02	<0.01	0.016	<0.01	<0.01	4.95	0.05	0.001	0.07	0.73
635225	Drill Core	1.21	<0.001	<0.001	0.06	0.03	<2	<0.001	<0.001	0.07	3.17	<0.02	0.02	<0.001	<0.01	<0.01	33.19	0.02	<0.001	0.10	<0.01
635226	Drill Core	1.98	<0.001	<0.001	0.09	0.13	<2	<0.001	<0.001	0.08	1.37	<0.02	0.02	<0.001	<0.01	<0.01	35.20	0.03	<0.001	0.14	0.05
635227	Drill Core	1.82	<0.001	<0.001	0.31	0.55	<2	0.002	<0.001	0.04	0.61	<0.02	0.01	0.001	<0.01	<0.01	19.28	0.06	<0.001	0.08	0.26
635228	Drill Core	1.61	0.001	0.003	1.02	2.20	<2	0.006	<0.001	0.03	2.63	<0.02	<0.01	0.006	<0.01	<0.01	9.27	0.09	0.002	0.11	0.85
635229	Drill Core	1.96	0.002	0.003	0.80	2.76	<2	0.006	<0.001	0.03	2.53	<0.02	<0.01	0.007	<0.01	<0.01	12.25	0.08	0.002	0.12	0.87
635230	Rock	0.38	<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	0.02	0.17	<0.02	<0.01	<0.001	<0.01	<0.01	21.36	0.03	<0.001	11.06	0.12
635231	Drill Core	2.43	0.002	0.003	1.45	4.51	<2	0.004	<0.001	0.05	3.73	<0.02	0.01	0.012	<0.01	<0.01	23.54	0.03	<0.001	0.10	0.36
635232	Drill Core	0.82	0.001	0.002	1.88	8.82	<2	0.002	<0.001	0.04	1.00	<0.02	0.02	0.024	<0.01	<0.01	25.43	0.02	<0.001	0.07	0.19
635233	Drill Core	1.30	0.001	0.003	2.49	7.29	<2	0.006	<0.001	0.02	3.68	<0.02	<0.01	0.019	<0.01	<0.01	5.42	0.07	0.001	0.09	0.68
635234	Drill Core	2.14	0.002	0.002	0.92	2.03	<2	0.007	<0.001	0.03	1.68	<0.02	0.01	0.005	<0.01	<0.01	14.96	0.06	0.002	0.12	0.85
635235	Drill Core	0.81	0.003	0.008	0.98	6.77	3	0.008	<0.001	0.03	6.40	<0.02	0.01	0.016	<0.01	<0.01	11.72	0.04	0.002	0.09	0.65
635236	Drill Core	1.46	<0.001	<0.001	0.34	0.38	<2	0.002	<0.001	0.04	0.61	<0.02	0.02	<0.001	<0.01	<0.01	31.57	0.02	<0.001	0.09	0.17
635237	Drill Core	1.15	0.001	0.003	1.98	8.01	<2	0.002	<0.001	0.02	1.16	<0.02	<0.01	0.018	<0.01	<0.01	9.50	0.02	<0.001	0.06	0.27
635238	Drill Core	1.66	0.003	0.004	0.74	8.66	<2	0.008	<0.001	0.02	2.25	<0.02	<0.01	0.021	<0.01	<0.01	6.33	0.08	0.002	0.13	1.03
635239	Drill Core	1.41	0.002	0.004	1.10	11.19	<2	0.005	<0.001	0.02	1.67	<0.02	<0.01	0.026	<0.01	<0.01	6.99	0.05	0.001	0.08	0.59
635240	Rock Pulp	0.06	0.001	0.674	6.14	6.68	70	<0.001	<0.001	0.10	4.93	<0.02	0.02	0.019	0.04	<0.01	1.41	0.02	0.001	0.26	5.32



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: December 16, 2010

Page: 4 of 6 **Part** 2

CERTIFICATE OF ANALYSIS

WHI10000668.1

	Method	7TD	7TD	7TD	7TD	G8SG
	Analyte	Na	K	W	S	SG
	Unit	%	%	%	%	
	MDL	0.01	0.01	0.01	0.05	0
635211	Drill Core	<0.01	0.96	<0.01	1.34	2.24
635212	Drill Core	<0.01	0.64	<0.01	9.51	2.59
635213	Drill Core	<0.01	0.82	<0.01	14.31	2.48
635214	Drill Core	<0.01	0.08	<0.01	17.60	2.86
635215	Drill Core	<0.01	0.18	<0.01	15.76	2.86
635216	Drill Core	<0.01	0.22	<0.01	8.02	2.63
635217	Drill Core	<0.01	0.28	<0.01	3.92	2.52
635218	Drill Core	0.05	0.42	<0.01	6.99	2.52
635219	Drill Core	0.04	0.33	<0.01	2.35	2.35
635220	Drill Core	0.04	0.40	<0.01	1.16	2.30
635221	Drill Core	0.03	0.38	<0.01	1.04	2.30
635222	Drill Core	0.02	0.61	<0.01	1.83	2.22
635223	Drill Core	<0.01	1.21	<0.01	3.36	2.10
635224	Drill Core	<0.01	0.45	<0.01	17.58	2.62
635225	Drill Core	<0.01	0.02	<0.01	3.35	2.55
635226	Drill Core	0.01	0.06	<0.01	1.26	2.47
635227	Drill Core	<0.01	0.15	<0.01	0.71	2.47
635228	Drill Core	<0.01	0.56	<0.01	3.98	2.43
635229	Drill Core	<0.01	0.55	<0.01	4.08	2.48
635230	Rock	0.03	0.05	<0.01	<0.05	2.61
635231	Drill Core	0.03	0.23	<0.01	5.83	2.52
635232	Drill Core	0.03	0.13	<0.01	5.27	2.55
635233	Drill Core	0.02	0.39	<0.01	8.02	2.52
635234	Drill Core	0.01	0.53	<0.01	2.71	2.33
635235	Drill Core	0.01	0.41	<0.01	10.62	2.62
635236	Drill Core	0.02	0.12	<0.01	0.55	2.44
635237	Drill Core	0.01	0.16	<0.01	5.29	2.55
635238	Drill Core	0.01	0.61	<0.01	6.79	2.34
635239	Drill Core	<0.01	0.34	<0.01	7.42	2.48
635240	Rock Pulp	2.20	1.36	<0.01	5.12	N.A.



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: December 16, 2010

Page: 5 of 6 Part 1

CERTIFICATE OF ANALYSIS

WHI10000668.1

	Method Analyte Unit MDL	WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD
		Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg	Al
		kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%	%
		0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01	0.01
635241	Drill Core	1.10	<0.001	0.001	0.24	1.39	<2	0.003	<0.001	0.04	0.58	<0.02	0.02	0.004	<0.01	<0.01	29.59	0.03	<0.001	0.09	0.29
635242	Drill Core	1.47	0.003	0.006	1.45	6.98	<2	0.007	<0.001	0.01	1.91	<0.02	<0.01	0.019	<0.01	<0.01	3.78	0.07	0.001	0.10	0.82
635243	Drill Core	1.60	0.002	0.002	0.32	2.08	<2	0.005	<0.001	0.03	0.74	<0.02	0.01	0.004	<0.01	<0.01	23.50	0.07	0.001	0.13	0.66
635244	Drill Core	2.34	0.002	0.003	0.04	0.02	<2	0.005	<0.001	0.04	2.01	<0.02	0.02	<0.001	<0.01	<0.01	22.46	0.06	0.001	0.14	0.66
635245	Drill Core	2.47	0.001	0.002	<0.02	0.04	<2	0.004	<0.001	0.04	0.54	<0.02	0.02	<0.001	<0.01	<0.01	26.56	0.05	<0.001	0.11	0.57
635246	Drill Core	1.04	0.003	0.004	0.03	0.31	<2	0.008	<0.001	0.02	1.03	<0.02	0.01	<0.001	<0.01	<0.01	12.06	0.07	0.002	0.15	1.25
635247	Drill Core	2.58	0.003	0.004	0.08	0.15	<2	0.008	<0.001	0.02	1.73	<0.02	0.01	<0.001	<0.01	<0.01	11.74	0.05	0.002	0.14	1.10
635248	Drill Core	1.32	0.004	0.003	1.97	0.26	4	0.009	<0.001	0.04	0.75	<0.02	0.01	<0.001	<0.01	<0.01	16.23	0.06	0.002	0.20	1.24
635249	Drill Core	1.06	0.008	0.006	0.30	1.63	2	0.018	<0.001	0.01	1.28	<0.02	<0.01	0.003	<0.01	<0.01	4.51	0.08	0.005	0.26	2.42
635250	Drill Core	0.67	0.002	0.004	0.21	0.17	<2	0.005	<0.001	0.02	1.49	<0.02	<0.01	<0.001	<0.01	<0.01	8.00	0.04	0.001	0.07	0.47
634251	Drill Core	0.69	0.001	0.004	0.16	0.15	<2	0.005	<0.001	0.02	2.28	<0.02	<0.01	<0.001	<0.01	<0.01	8.72	0.03	<0.001	0.06	0.35
634252	Drill Core	2.22	0.002	0.003	0.19	0.86	<2	0.006	<0.001	0.02	1.08	<0.02	<0.01	0.002	<0.01	<0.01	5.73	0.12	0.001	0.10	0.69
634253	Drill Core	1.07	0.001	0.005	0.22	0.31	<2	0.005	<0.001	0.06	2.28	<0.02	0.01	<0.001	<0.01	<0.01	25.60	0.18	<0.001	0.12	0.26
634254	Drill Core	1.34	0.005	0.007	0.59	3.68	2	0.012	<0.001	0.02	1.34	<0.02	<0.01	0.008	<0.01	<0.01	9.35	0.29	0.003	0.14	1.03
634255	Drill Core	1.86	0.005	0.014	0.08	0.32	<2	0.009	<0.001	0.03	0.67	<0.02	0.02	<0.001	<0.01	<0.01	21.69	1.16	0.003	0.10	0.50
634256	Drill Core	1.10	0.002	0.006	0.02	0.07	<2	0.005	<0.001	0.04	0.84	<0.02	0.02	<0.001	<0.01	<0.01	31.13	0.23	<0.001	0.14	0.22
634257	Drill Core	1.64	0.004	0.007	0.10	0.33	<2	0.007	<0.001	0.03	0.49	<0.02	0.02	<0.001	<0.01	<0.01	25.91	0.19	0.002	0.11	0.51
634258	Drill Core	1.42	0.003	0.008	1.37	1.49	5	0.008	<0.001	0.04	2.44	<0.02	0.02	0.004	<0.01	<0.01	22.66	0.44	0.003	0.12	0.64
634259	Drill Core	1.59	0.004	0.006	0.18	0.84	<2	0.008	<0.001	0.01	0.81	<0.02	<0.01	0.002	<0.01	<0.01	7.12	0.46	0.002	0.08	0.61
634260	Rock	0.26	<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	0.02	0.15	<0.02	0.01	<0.001	<0.01	<0.01	20.85	0.03	<0.001	11.17	0.10
634261	Drill Core	1.90	0.004	0.009	0.40	1.30	2	0.011	<0.001	0.01	1.54	<0.02	<0.01	0.001	<0.01	<0.01	2.95	0.21	0.003	0.09	0.81
634262	Drill Core	1.72	0.008	0.013	0.39	1.91	4	0.016	<0.001	0.01	0.97	<0.02	<0.01	0.004	<0.01	<0.01	8.19	0.39	0.005	0.16	1.18
634263	Drill Core	1.35	0.011	0.017	0.06	0.92	<2	0.020	<0.001	<0.01	1.27	<0.02	<0.01	0.001	<0.01	<0.01	2.06	0.14	0.005	0.17	1.50
634264	Drill Core	2.67	0.007	0.012	1.31	0.56	6	0.025	<0.001	<0.01	1.36	<0.02	<0.01	<0.001	<0.01	<0.01	5.88	1.81	0.009	0.23	1.99
634265	Drill Core	0.86	<0.001	0.002	0.27	0.03	<2	0.012	<0.001	0.03	2.60	<0.02	0.02	<0.001	<0.01	<0.01	16.87	0.53	0.004	0.36	2.50
634266	Drill Core	1.81	<0.001	0.002	<0.02	<0.01	<2	0.003	<0.001	0.05	1.96	<0.02	0.02	<0.001	<0.01	<0.01	27.94	0.02	0.002	0.33	1.85
634267	Drill Core	1.46	0.001	0.002	<0.02	<0.01	<2	0.010	<0.001	0.04	1.53	<0.02	0.02	<0.001	<0.01	<0.01	22.01	0.02	0.003	0.36	2.64
634268	Drill Core	1.74	0.013	0.010	0.03	0.08	3	0.029	0.002	0.01	7.84	0.02	0.01	<0.001	<0.01	<0.01	8.75	2.72	0.011	0.34	3.24
634269	Drill Core	1.43	0.009	0.009	0.10	1.12	2	0.030	0.001	<0.01	3.26	<0.02	<0.01	0.006	<0.01	<0.01	2.01	0.20	0.014	0.42	4.07
634270	Rock Pulp	0.06	<0.001	0.502	1.49	4.40	28	0.001	0.001	0.67	5.55	<0.02	0.01	0.028	<0.01	<0.01	4.41	0.05	0.003	1.56	4.77



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: Selwyn Resources Ltd.
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: December 16, 2010

Page: 5 of 6 **Part** 2

CERTIFICATE OF ANALYSIS

WHI10000668.1

	Method	7TD	7TD	7TD	7TD	G8SG
Analyte	Na	K	W	S	SG	
Unit	%	%	%	%		
MDL	0.01	0.01	0.01	0.05	0	
635241	Drill Core	<0.01	0.18	<0.01	0.98	2.41
635242	Drill Core	<0.01	0.49	<0.01	5.70	2.40
635243	Drill Core	<0.01	0.42	<0.01	1.58	2.36
635244	Drill Core	0.01	0.39	<0.01	2.00	2.38
635245	Drill Core	0.01	0.35	<0.01	0.23	2.42
635246	Drill Core	0.01	0.80	<0.01	1.07	2.44
635247	Drill Core	0.01	0.70	<0.01	1.81	2.42
635248	Drill Core	<0.01	0.76	<0.01	0.95	2.36
635249	Drill Core	<0.01	1.03	<0.01	1.99	2.24
635250	Drill Core	0.01	0.30	<0.01	1.43	2.48
634251	Drill Core	0.01	0.24	<0.01	2.35	2.58
634252	Drill Core	<0.01	0.42	<0.01	1.27	2.43
634253	Drill Core	<0.01	0.15	<0.01	3.03	2.54
634254	Drill Core	<0.01	0.60	<0.01	3.63	2.41
634255	Drill Core	<0.01	0.28	<0.01	0.85	2.47
634256	Drill Core	<0.01	0.13	<0.01	1.01	2.52
634257	Drill Core	<0.01	0.29	<0.01	0.67	2.50
634258	Drill Core	<0.01	0.36	<0.01	3.83	2.54
634259	Drill Core	<0.01	0.35	<0.01	1.22	2.46
634260	Rock	<0.01	0.02	<0.01	<0.05	2.75
634261	Drill Core	<0.01	0.48	<0.01	2.13	2.44
634262	Drill Core	<0.01	0.69	<0.01	2.13	2.31
634263	Drill Core	<0.01	0.88	<0.01	1.72	2.23
634264	Drill Core	<0.01	1.28	<0.01	1.92	2.15
634265	Drill Core	<0.01	1.00	<0.01	2.99	2.41
634266	Drill Core	<0.01	0.83	<0.01	2.34	2.63
634267	Drill Core	<0.01	0.91	<0.01	1.66	2.41
634268	Drill Core	<0.01	1.79	<0.01	9.36	2.31
634269	Drill Core	<0.01	2.16	<0.01	4.19	1.91
634270	Rock Pulp	0.10	2.89	<0.01	5.44	N.A.



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: December 16, 2010

Page: 6 of 6 **Part** 1

CERTIFICATE OF ANALYSIS

WHI10000668.1

	Method Analyte Unit MDL	WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD
		Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg	Al
		kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%	%
		0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01	0.01
634271	Drill Core	2.20	0.006	0.011	0.14	0.34	<2	0.029	0.001	<0.01	2.95	<0.02	<0.01	0.002	<0.01	<0.01	2.16	0.28	0.015	0.41	4.36



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: December 16, 2010

Page: 6 of 6 **Part** 2

CERTIFICATE OF ANALYSIS

WHI10000668.1

Method		7TD	7TD	7TD	7TD	G8SG
Analyte		Na	K	W	S	SG
Unit		%	%	%	%	
MDL		0.01	0.01	0.01	0.05	0
634271	Drill Core	<0.01	2.60	<0.01	3.63	1.96



Acme Analytical Laboratories (Vancouver) Ltd.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: **Selwyn Resources Ltd.**

Suite 700 - 509 Richards Street

Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: December 16, 2010

Page: 1 of 2 Part 1

QUALITY CONTROL REPORT

WHI10000668.1

	Method Analyte Unit MDL	WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD
		Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg	Al
		kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%	%
		0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01	0.01
Pulp Duplicates																					
635208	Drill Core	1.50	<0.001	0.003	<0.02	0.19	<2	0.009	<0.001	<0.01	0.66	<0.02	<0.01	<0.001	<0.01	<0.01	5.27	1.56	0.002	0.10	1.07
REP 635208	QC		<0.001	0.003	<0.02	0.19	<2	0.009	<0.001	<0.01	0.66	<0.02	<0.01	<0.001	<0.01	<0.01	5.19	1.55	0.003	0.10	1.05
635233	Drill Core	1.30	0.001	0.003	2.49	7.29	<2	0.006	<0.001	0.02	3.68	<0.02	<0.01	0.019	<0.01	<0.01	5.42	0.07	0.001	0.09	0.68
REP 635233	QC		0.002	0.003	2.49	7.32	<2	0.006	<0.001	0.02	3.71	<0.02	<0.01	0.020	<0.01	<0.01	5.48	0.07	0.001	0.10	0.69
634254	Drill Core	1.34	0.005	0.007	0.59	3.68	2	0.012	<0.001	0.02	1.34	<0.02	<0.01	0.008	<0.01	<0.01	9.35	0.29	0.003	0.14	1.03
REP 634254	QC		0.005	0.007	0.59	3.63	3	0.012	<0.001	0.02	1.35	<0.02	<0.01	0.008	<0.01	<0.01	9.38	0.28	0.003	0.14	1.02
Core Reject Duplicates																					
635182	Drill Core	2.44	0.001	0.003	0.10	0.07	<2	0.005	<0.001	0.04	1.38	<0.02	0.01	<0.001	<0.01	<0.01	23.35	0.06	0.002	0.13	0.83
DUP 635182	QC		0.002	0.003	0.11	0.07	<2	0.005	<0.001	0.03	1.40	<0.02	0.01	<0.001	<0.01	<0.01	22.51	0.06	0.002	0.13	0.85
635217	Drill Core	1.42	0.002	0.002	0.29	2.39	<2	0.004	<0.001	0.05	2.22	<0.02	0.01	0.007	<0.01	<0.01	25.44	0.03	<0.001	0.16	0.42
DUP 635217	QC		0.001	0.003	0.30	2.31	<2	0.004	<0.001	0.06	2.27	<0.02	0.01	0.007	<0.01	<0.01	26.34	0.02	<0.001	0.17	0.42
634252	Drill Core	2.22	0.002	0.003	0.19	0.86	<2	0.006	<0.001	0.02	1.08	<0.02	<0.01	0.002	<0.01	<0.01	5.73	0.12	0.001	0.10	0.69
DUP 634252	QC		0.002	0.003	0.19	0.86	<2	0.007	<0.001	0.02	0.88	<0.02	<0.01	0.001	<0.01	<0.01	5.52	0.13	0.001	0.10	0.70
Reference Materials																					
STD OREAS131A	Standard		<0.001	0.034	1.77	2.85	31	0.003	0.002	0.17	6.00	<0.02	<0.01	0.008	<0.01	<0.01	5.31	0.06	0.002	3.11	4.62
STD OREAS131A	Standard		<0.001	0.032	1.72	2.92	32	0.003	0.002	0.17	5.77	<0.02	<0.01	0.008	<0.01	<0.01	5.36	0.05	0.002	3.17	4.67
STD OREAS131A	Standard		<0.001	0.032	1.67	2.86	30	0.002	0.002	0.17	5.76	<0.02	<0.01	0.008	<0.01	<0.01	5.24	0.05	0.002	3.12	4.62
STD OREAS131A	Standard		<0.001	0.032	1.76	2.94	31	0.003	0.002	0.17	5.80	<0.02	<0.01	0.008	<0.01	<0.01	5.41	0.06	0.002	3.20	4.74
STD OREAS131A	Standard		<0.001	0.032	1.70	2.87	31	0.003	0.002	0.17	5.78	<0.02	<0.01	0.008	<0.01	<0.01	5.28	0.05	0.003	3.14	4.65
STD R4T	Standard		0.065	0.516	1.59	3.46	85	0.355	0.043	0.09	24.15	<0.02	0.02	0.021	0.01	<0.01	2.28	0.04	0.019	1.44	4.02
STD R4T	Standard		0.064	0.502	1.54	3.41	86	0.349	0.040	0.09	23.78	<0.02	0.02	0.019	0.02	<0.01	2.20	0.05	0.018	1.42	3.96
STD R4T	Standard		0.064	0.512	1.55	3.47	87	0.353	0.041	0.08	24.12	<0.02	0.02	0.021	0.01	<0.01	2.20	0.04	0.019	1.42	4.01
STD R4T	Standard		0.064	0.505	1.56	3.26	88	0.353	0.041	0.09	24.09	<0.02	0.02	0.019	0.01	<0.01	2.10	0.05	0.018	1.43	3.98
STD R4T	Standard		0.064	0.513	1.57	3.48	89	0.356	0.041	0.09	24.19	<0.02	0.02	0.019	0.01	<0.01	2.21	0.04	0.018	1.43	3.99
STD SU-1B	Standard		<0.001	1.234	<0.02	0.03	7	2.034	0.070	0.07	25.62	<0.02	0.03	0.001	<0.01	<0.01	2.33	0.06	0.033	1.83	4.52
STD SU-1B	Standard		<0.001	1.175	<0.02	0.03	7	1.953	0.067	0.07	25.21	<0.02	0.03	<0.001	<0.01	<0.01	2.24	0.06	0.033	1.82	4.43
STD SU-1B	Standard		<0.001	1.208	<0.02	0.03	6	2.034	0.069	0.07	25.76	<0.02	0.03	<0.001	<0.01	<0.01	2.26	0.07	0.032	1.83	4.51
STD SU-1B	Standard		<0.001	1.169	<0.02	0.03	6	1.963	0.066	0.07	25.02	<0.02	0.03	<0.001	<0.01	<0.01	2.22	0.06	0.031	1.80	4.41



Acme Analytical Laboratories (Vancouver) Ltd.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: Selwyn Resources Ltd.

Suite 700 - 509 Richards Street

Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: December 16, 2010

Page: 1 of 2 **Part** 2

QUALITY CONTROL REPORT

WHI10000668.1

Method		7TD	7TD	7TD	7TD	G8SG
Analyte		Na	K	W	S	SG
Unit		%	%	%	%	%
MDL		0.01	0.01	0.01	0.05	0
Pulp Duplicates						
635208	Drill Core	<0.01	0.68	<0.01	0.65	2.30
REP 635208	QC	<0.01	0.67	<0.01	0.64	
635233	Drill Core	0.02	0.39	<0.01	8.02	2.52
REP 635233	QC	0.02	0.40	<0.01	8.02	
634254	Drill Core	<0.01	0.60	<0.01	3.63	2.41
REP 634254	QC	<0.01	0.60	<0.01	3.52	
Core Reject Duplicates						
635182	Drill Core	<0.01	0.44	<0.01	1.60	2.43
DUP 635182	QC	<0.01	0.44	<0.01	1.68	2.44
635217	Drill Core	<0.01	0.28	<0.01	3.92	2.52
DUP 635217	QC	0.11	0.29	<0.01	3.54	2.52
634252	Drill Core	<0.01	0.42	<0.01	1.27	2.43
DUP 634252	QC	<0.01	0.42	<0.01	1.21	2.42
Reference Materials						
STD OREAS131A	Standard	0.15	3.30	<0.01	5.18	
STD OREAS131A	Standard	0.15	3.29	<0.01	4.64	
STD OREAS131A	Standard	0.15	3.08	<0.01	5.10	
STD OREAS131A	Standard	0.16	3.22	<0.01	4.85	
STD OREAS131A	Standard	0.15	3.38	<0.01	4.63	
STD R4T	Standard	0.93	1.15	<0.01	11.76	
STD R4T	Standard	0.89	1.15	<0.01	11.48	
STD R4T	Standard	0.91	1.18	<0.01	12.60	
STD R4T	Standard	0.91	1.17	<0.01	11.98	
STD R4T	Standard	0.91	1.18	<0.01	13.01	
STD SU-1B	Standard	1.72	0.63	<0.01	8.39	
STD SU-1B	Standard	1.66	0.62	<0.01	8.20	
STD SU-1B	Standard	1.74	0.63	<0.01	8.95	
STD SU-1B	Standard	1.67	0.61	<0.01	9.01	



Acme Analytical Laboratories (Vancouver) Ltd.
1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: December 16, 2010

Page: 2 of 2 Part 1

QUALITY CONTROL REPORT

WHI10000668.1

			WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	
			Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg	Al
			kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%	%
			0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01	0.01
STD R4T Expected				0.062	0.502	1.518	3.376	86	0.339	0.039	0.086	24.07	0.0087	0.0185	0.018	0.0138	0.0018	2.166	0.045	0.018	1.384	3.897
STD OREAS131A Expected				0.001	0.0322	1.72	2.83	30.9	0.0027	0.0023	0.1722	5.8166	0.0082	0.0028	0.0081	0.0047	0.001	5.286	0.0536	0.0025	3.1182	4.6057
STD SU-1B Expected				0.0004	1.185	0.0058	0.0235	6.4	1.97	0.0672	0.0703	25.54	0.00025	0.03	0.0003	0.00002	0.0003	2.21	0.06	0.032	1.79	4.39
BLK	Blank		<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	<0.01	<0.01	<0.02	<0.01	<0.001	<0.01	<0.01	<0.01	<0.01	<0.01	<0.001	<0.01	<0.01
BLK	Blank		<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	<0.01	<0.01	<0.02	<0.01	<0.001	<0.01	<0.01	<0.01	<0.01	<0.01	<0.001	<0.01	<0.01
BLK	Blank		<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	<0.01	<0.01	<0.02	<0.01	<0.001	<0.01	<0.01	<0.01	<0.01	<0.01	<0.001	<0.01	<0.01
BLK	Blank		<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	<0.01	<0.01	<0.02	<0.01	<0.001	<0.01	<0.01	<0.01	<0.01	<0.01	<0.001	<0.01	<0.01
BLK	Blank		<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	<0.01	<0.01	<0.02	<0.01	<0.001	<0.01	<0.01	<0.01	<0.01	<0.01	<0.001	<0.01	<0.01
Prep Wash																						
G1	Prep Blank		<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	0.08	2.42	<0.02	0.08	0.002	<0.01	<0.01	2.40	0.08	<0.001	0.65	7.84	
G1	Prep Blank		<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	0.08	2.40	<0.02	0.07	0.002	<0.01	<0.01	2.37	0.08	<0.001	0.65	7.62	



Acme Analytical Laboratories (Vancouver) Ltd.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: **Selwyn Resources Ltd.**

Suite 700 - 509 Richards Street

Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: December 16, 2010

Page: 2 of 2 **Part** 2

QUALITY CONTROL REPORT

WHI10000668.1

		7TD Na %	7TD K %	7TD W %	7TD S %	G8SG SG %
		0.01	0.01	0.01	0.05	0
STD R4T Expected		0.9	1.153	0.00016	12.9903	
STD OREAS131A Expected		0.1501	3.1584	0.0005	4.8	
STD SU-1B Expected		1.662	0.6	0.0007	8.76	
BLK	Blank	<0.01	<0.01	<0.01	<0.05	
BLK	Blank	<0.01	<0.01	<0.01	<0.05	
BLK	Blank	<0.01	<0.01	<0.01	<0.05	
BLK	Blank	<0.01	<0.01	<0.01	<0.05	
BLK	Blank	<0.01	<0.01	<0.01	<0.05	
Prep Wash						
G1	Prep Blank	2.71	2.99	<0.01	0.05	2.69
G1	Prep Blank	2.75	2.94	<0.01	<0.05	2.68



1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: Selwyn Resources Ltd.

Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Submitted By: Jason K. Dunning

Receiving Lab: Canada-Whitehorse

Received: November 23, 2010

Report Date: December 06, 2010

Page: 1 of 3

CERTIFICATE OF ANALYSIS

WHI10000664.1

CLIENT JOB INFORMATION

Project: Selwyn Project
Shipment ID:
P.O. Number: 1081
Number of Samples: 38

SAMPLE DISPOSAL

STOR-PLP Store After 90 days Invoice for Storage
STOR-RJT Store After 90 days Invoice for Storage

Acme does not accept responsibility for samples left at the laboratory after 90 days without prior written instructions for sample storage or return.

Invoice To: Selwyn Resources Ltd.
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6
Canada

CC:

SAMPLE PREPARATION AND ANALYTICAL PROCEDURES

Method Code	Number of Samples	Code Description	Test Wgt (g)	Report Status	Lab
R200-250	37	Crush split and pulverize 250g drill core to 200 mesh			WHI
7TD2	38	4 Acid digestion ICP-ES analysis.	0.5	Completed	VAN
G812	38	Specific Gravity on Pulp		Completed	VAN

ADDITIONAL COMMENTS



This report supersedes all previous preliminary and final reports with this file number dated prior to the date on this certificate. Signature indicates final approval; preliminary reports are unsigned and should be used for reference only.

All results are considered the confidential property of the client. Acme assumes the liabilities for actual cost of analysis only.

“**” asterisk indicates that an analytical result could not be provided due to unusually high levels of interference from other elements.



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: December 06, 2010

Page: 2 of 3 Part 1

CERTIFICATE OF ANALYSIS

WHI10000664.1

	Method Analyte Unit MDL	WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD
		Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg	Al
		kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%	%
		0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01	0.01
635401	Drill Core	2.03	0.002	0.005	<0.02	0.47	<2	0.009	<0.001	<0.01	0.81	<0.02	<0.01	0.002	<0.01	<0.01	2.54	0.96	0.003	0.16	1.56
635402	Drill Core	1.68	0.004	0.005	0.12	0.37	<2	0.011	<0.001	<0.01	1.24	<0.02	<0.01	0.002	<0.01	<0.01	1.65	0.34	0.003	0.15	1.65
635403	Drill Core	1.99	0.003	0.007	1.98	4.89	3	0.007	<0.001	0.03	3.95	<0.02	<0.01	0.024	<0.01	<0.01	9.56	0.03	0.002	0.11	0.96
635404	Drill Core	1.42	0.002	0.006	1.82	12.71	<2	0.004	<0.001	0.01	3.47	<0.02	<0.01	0.059	<0.01	<0.01	0.28	0.02	<0.001	0.05	0.58
635405	Drill Core	0.85	<0.001	0.005	6.83	14.29	<2	0.002	<0.001	<0.01	5.99	<0.02	<0.01	0.072	<0.01	<0.01	0.74	0.02	<0.001	0.04	0.39
635406	Drill Core	1.99	0.003	0.008	2.11	9.65	2	0.010	<0.001	0.02	7.53	<0.02	<0.01	0.027	<0.01	<0.01	0.32	0.05	0.002	0.09	1.00
635407	Drill Core	1.43	0.003	0.007	2.87	10.59	<2	0.008	<0.001	0.02	4.73	<0.02	<0.01	0.029	<0.01	<0.01	1.51	0.06	0.001	0.08	1.04
635408	Drill Core	0.92	<0.001	0.002	0.21	1.21	<2	0.003	<0.001	0.04	0.94	<0.02	0.01	0.003	<0.01	<0.01	21.67	0.04	<0.001	0.08	0.32
635409	Drill Core	1.80	0.001	0.002	0.11	0.49	<2	0.003	<0.001	0.01	1.59	<0.02	<0.01	0.001	<0.01	<0.01	3.61	0.03	<0.001	0.04	0.33
635410	Drill Core	0.88	<0.001	<0.001	0.02	0.32	<2	0.002	<0.001	0.01	0.55	<0.02	<0.01	<0.001	<0.01	<0.01	9.02	0.02	<0.001	0.04	0.22
635411	Drill Core	0.83	<0.001	<0.001	0.02	0.21	<2	0.002	<0.001	0.02	0.56	<0.02	<0.01	<0.001	<0.01	<0.01	11.08	0.02	<0.001	0.04	0.25
635412	Drill Core	2.87	0.002	0.007	1.10	0.92	<2	0.008	<0.001	0.02	3.94	<0.02	<0.01	0.003	<0.01	<0.01	8.92	0.04	0.001	0.08	0.73
635413	Drill Core	2.29	0.006	0.005	2.68	2.27	<2	0.014	<0.001	<0.01	2.23	<0.02	<0.01	0.006	<0.01	<0.01	2.39	0.03	0.001	0.10	1.32
635414	Drill Core	0.79	0.004	0.017	4.70	17.27	4	0.009	<0.001	0.04	8.68	<0.02	<0.01	0.060	<0.01	<0.01	6.26	0.06	0.001	0.08	0.86
635415	Drill Core	0.52	<0.001	0.010	1.88	29.85	<2	0.001	<0.001	0.03	1.46	<0.02	<0.01	0.078	<0.01	<0.01	10.90	0.03	<0.001	0.03	0.12
635416	Drill Core	1.99	<0.001	<0.001	0.57	0.74	<2	0.001	<0.001	0.08	1.09	<0.02	0.02	0.002	<0.01	<0.01	31.44	0.03	<0.001	0.13	0.08
635417	Drill Core	1.84	<0.001	<0.001	0.14	0.29	<2	0.001	<0.001	0.05	3.01	<0.02	0.01	<0.001	<0.01	<0.01	25.32	0.04	<0.001	0.10	0.19
635418	Drill Core	1.58	<0.001	0.003	1.76	4.80	<2	0.006	<0.001	0.02	3.05	<0.02	<0.01	0.013	<0.01	<0.01	5.92	0.08	0.002	0.10	0.81
635419	Drill Core	2.27	<0.001	0.002	0.94	3.47	<2	0.003	<0.001	0.06	2.19	<0.02	0.01	0.010	<0.01	<0.01	26.22	0.03	<0.001	0.10	0.25
635420	Rock	0.27	<0.001	<0.001	<0.02	0.02	<2	<0.001	<0.001	0.02	0.14	<0.02	0.01	<0.001	<0.01	<0.01	22.32	0.02	<0.001	11.47	0.07
635421	Drill Core	1.26	0.002	0.005	4.62	17.39	3	0.004	<0.001	0.03	3.17	<0.02	<0.01	0.043	<0.01	<0.01	16.50	0.03	<0.001	0.07	0.33
635422	Drill Core	3.05	0.001	0.003	0.75	3.61	<2	0.006	<0.001	0.03	2.62	<0.02	<0.01	0.008	<0.01	<0.01	14.54	0.05	<0.001	0.09	0.54
635423	Drill Core	1.48	0.002	0.003	2.22	2.38	<2	0.005	<0.001	0.04	1.82	<0.02	0.01	0.006	<0.01	<0.01	22.88	0.04	0.001	0.12	0.58
635424	Drill Core	2.95	0.003	0.009	2.71	8.76	3	0.009	<0.001	0.04	6.99	<0.02	<0.01	0.025	<0.01	<0.01	14.37	0.04	0.001	0.11	0.67
635425	Drill Core	2.53	0.002	0.003	1.10	5.26	<2	0.004	<0.001	0.03	1.84	<0.02	<0.01	0.015	<0.01	<0.01	15.17	0.05	<0.001	0.10	0.56
635426	Drill Core	2.89	0.002	0.005	0.73	4.47	<2	0.007	<0.001	0.03	1.31	<0.02	0.01	0.013	<0.01	<0.01	16.62	0.07	0.002	0.13	0.86
635427	Drill Core	0.51	<0.001	0.004	6.97	10.86	<2	0.002	<0.001	0.02	0.97	<0.02	<0.01	0.050	<0.01	<0.01	10.43	0.05	<0.001	0.04	0.18
635428	Drill Core	3.16	0.002	0.004	0.20	0.13	<2	0.006	<0.001	0.03	1.68	<0.02	0.01	<0.001	<0.01	<0.01	16.70	0.07	0.002	0.13	0.90
635429	Drill Core	2.00	0.001	0.003	0.16	0.85	<2	0.005	<0.001	<0.01	1.32	<0.02	<0.01	0.002	<0.01	<0.01	2.94	0.05	<0.001	0.07	0.56
635430	Rock Pulp	0.06	<0.001	0.660	5.98	7.03	71	<0.001	<0.001	0.09	4.78	<0.02	0.02	0.019	0.03	<0.01	1.15	0.02	0.001	0.23	3.59



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: December 06, 2010

Page: 2 of 3 **Part** 2

CERTIFICATE OF ANALYSIS

WHI10000664.1

	Method	7TD	7TD	7TD	7TD	G8SG
	Analyte	Na	K	W	S	SG
	Unit	%	%	%	%	
	MDL	0.01	0.01	0.01	0.05	0
635401	Drill Core	<0.01	0.89	<0.01	0.96	2.25
635402	Drill Core	<0.01	0.97	<0.01	1.42	2.22
635403	Drill Core	<0.01	0.56	<0.01	7.33	2.46
635404	Drill Core	<0.01	0.36	<0.01	10.57	2.65
635405	Drill Core	<0.01	0.22	<0.01	14.71	2.87
635406	Drill Core	<0.01	0.54	<0.01	13.40	2.56
635407	Drill Core	<0.01	0.62	<0.01	11.13	2.53
635408	Drill Core	<0.01	0.20	<0.01	1.58	2.38
635409	Drill Core	<0.01	0.16	<0.01	1.73	2.40
635410	Drill Core	<0.01	0.12	<0.01	0.52	2.41
635411	Drill Core	<0.01	0.14	<0.01	0.51	2.39
635412	Drill Core	<0.01	0.42	<0.01	4.93	2.33
635413	Drill Core	<0.01	0.80	<0.01	3.78	2.19
635414	Drill Core	<0.01	0.51	<0.01	18.44	2.78
635415	Drill Core	<0.01	0.07	<0.01	15.33	2.92
635416	Drill Core	<0.01	0.07	<0.01	1.70	2.47
635417	Drill Core	<0.01	0.13	<0.01	3.64	2.54
635418	Drill Core	<0.01	0.47	<0.01	5.93	2.41
635419	Drill Core	<0.01	0.16	<0.01	4.32	2.55
635420	Rock	<0.01	0.03	<0.01	<0.05	2.63
635421	Drill Core	<0.01	0.19	<0.01	12.75	2.77
635422	Drill Core	<0.01	0.31	<0.01	4.70	2.45
635423	Drill Core	<0.01	0.36	<0.01	3.48	2.53
635424	Drill Core	<0.01	0.39	<0.01	12.92	2.67
635425	Drill Core	<0.01	0.33	<0.01	4.71	2.44
635426	Drill Core	<0.01	0.52	<0.01	3.60	2.39
635427	Drill Core	<0.01	0.11	<0.01	7.29	2.83
635428	Drill Core	<0.01	0.55	<0.01	1.92	2.31
635429	Drill Core	<0.01	0.32	<0.01	1.69	2.32
635430	Rock Pulp	2.30	1.36	<0.01	6.00	N.A.



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: December 06, 2010

Page: 3 of 3 **Part** 1

CERTIFICATE OF ANALYSIS

WHI10000664.1

	Method	WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD
	Analyte	Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg
	Unit	kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%
	MDL	0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01
635431	Drill Core	2.21	0.003	0.006	0.38	1.18	<2	0.009	<0.001	0.02	0.76	<0.02	<0.01	0.003	<0.01	<0.01	6.67	0.17	0.003	0.13
635432	Drill Core	2.87	0.003	0.004	0.28	1.19	<2	0.007	<0.001	0.07	1.31	<0.02	0.01	0.003	<0.01	<0.01	20.34	0.24	0.002	0.13
635433	Drill Core	2.94	0.002	0.003	0.16	0.44	<2	0.004	<0.001	0.04	0.47	<0.02	0.02	0.001	<0.01	<0.01	27.47	0.14	0.001	0.08
635434	Drill Core	2.00	0.006	0.013	0.15	1.23	<2	0.010	<0.001	0.03	1.13	<0.02	0.02	0.004	<0.01	<0.01	18.86	0.61	0.005	0.11
635435	Drill Core	2.85	0.004	0.007	2.64	1.73	5	0.009	<0.001	0.02	1.01	<0.02	0.02	0.004	<0.01	<0.01	15.07	0.89	0.004	0.10
635436	Drill Core	2.03	0.003	0.005	6.22	0.69	14	0.006	<0.001	0.02	1.08	<0.02	0.01	0.002	<0.01	<0.01	15.43	0.53	0.003	0.08
635437	Drill Core	1.45	0.003	0.012	0.04	0.24	<2	0.018	<0.001	0.02	3.34	<0.02	<0.01	<0.001	<0.01	<0.01	5.85	0.20	0.015	0.40
635438	Drill Core	0.74	0.002	0.007	<0.02	0.03	<2	0.021	<0.001	0.01	3.54	<0.02	<0.01	<0.001	<0.01	<0.01	4.03	0.12	0.022	0.61



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: December 06, 2010

Page: 3 of 3 **Part** 2

CERTIFICATE OF ANALYSIS

WHI10000664.1

	Method	7TD	7TD	7TD	7TD	G8SG
	Analyte	Na	K	W	S	SG
	Unit	%	%	%	%	
	MDL	0.01	0.01	0.01	0.05	0
635431	Drill Core	<0.01	0.66	<0.01	1.34	2.24
635432	Drill Core	<0.01	0.33	<0.01	2.27	2.28
635433	Drill Core	<0.01	0.17	<0.01	0.86	2.36
635434	Drill Core	<0.01	0.41	<0.01	2.01	2.22
635435	Drill Core	<0.01	0.46	<0.01	2.47	2.29
635436	Drill Core	<0.01	0.32	<0.01	2.55	2.44
635437	Drill Core	<0.01	2.88	<0.01	3.73	2.25
635438	Drill Core	<0.01	4.47	<0.01	3.66	2.29



Acme Analytical Laboratories (Vancouver) Ltd.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: **Selwyn Resources Ltd.**

Suite 700 - 509 Richards Street

Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: December 06, 2010

Page: 1 of 1 Part 1

QUALITY CONTROL REPORT

WHI10000664.1

	Method Analyte Unit MDL	WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD
		Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg	Al
		kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%	%
		0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01	0.01
Pulp Duplicates																					
REP 635411	QC		<0.001	<0.001	0.02	0.21	<2	0.002	<0.001	0.02	0.55	<0.02	<0.01	<0.001	<0.01	<0.01	11.00	0.02	<0.001	0.04	0.25
635438	Drill Core	0.74	0.002	0.007	<0.02	0.03	<2	0.021	<0.001	0.01	3.54	<0.02	<0.01	<0.001	<0.01	<0.01	4.03	0.12	0.022	0.61	5.90
REP 635438	QC		0.002	0.007	<0.02	0.03	<2	0.021	<0.001	0.01	3.47	<0.02	<0.01	<0.001	<0.01	<0.01	4.08	0.12	0.021	0.61	6.08
Core Reject Duplicates																					
635411	Drill Core	0.83	<0.001	<0.001	0.02	0.21	<2	0.002	<0.001	0.02	0.56	<0.02	<0.01	<0.001	<0.01	<0.01	11.08	0.02	<0.001	0.04	0.25
DUP 635411	QC		<0.001	<0.001	0.02	0.23	<2	0.002	<0.001	0.02	0.60	<0.02	<0.01	<0.001	<0.01	<0.01	11.24	0.02	<0.001	0.04	0.24
Reference Materials																					
STD OREAS131A	Standard		<0.001	0.033	1.76	2.94	31	0.003	0.002	0.17	5.81	<0.02	<0.01	0.008	<0.01	<0.01	5.38	0.05	0.002	3.21	4.74
STD OREAS131A	Standard		<0.001	0.032	1.69	2.90	31	0.003	0.002	0.18	5.94	<0.02	<0.01	0.008	<0.01	<0.01	5.48	0.06	0.003	3.13	4.60
STD R4T	Standard		0.065	0.519	1.60	3.50	89	0.359	0.041	0.09	24.57	<0.02	0.02	0.019	0.02	<0.01	2.26	0.04	0.019	1.46	4.08
STD R4T	Standard		0.063	0.504	1.51	3.44	86	0.345	0.040	0.09	24.41	<0.02	0.02	0.019	0.02	<0.01	2.19	0.05	0.018	1.39	3.87
STD SU-1B	Standard		<0.001	1.179	<0.02	0.04	8	2.001	0.067	0.07	25.49	<0.02	0.03	<0.001	<0.01	<0.01	2.25	0.06	0.031	1.83	4.47
STD SU-1B	Standard		<0.001	1.183	<0.02	0.03	6	1.944	0.068	0.07	25.93	<0.02	0.03	<0.001	<0.01	<0.01	2.24	0.08	0.031	1.79	4.38
STD R4T Expected			0.062	0.502	1.518	3.376	86	0.339	0.039	0.086	24.07	0.0087	0.0185	0.018	0.0138	0.0018	2.166	0.045	0.018	1.384	3.897
STD OREAS131A Expected			0.001	0.0322	1.72	2.83	30.9	0.0027	0.0023	0.1722	5.8166	0.0082	0.0028	0.0081	0.0047	0.001	5.286	0.0536	0.0025	3.1182	4.6057
STD SU-1B Expected			0.0004	1.185	0.0058	0.0235	6.4	1.97	0.0672	0.0703	25.54	0.00025	0.03	0.0003	0.00002	0.0003	2.21	0.06	0.032	1.79	4.39
BLK	Blank		<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	<0.01	<0.01	<0.02	<0.01	<0.001	<0.01	<0.01	<0.01	<0.01	<0.001	<0.01	
BLK	Blank		<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	<0.01	<0.01	<0.02	<0.01	<0.001	<0.01	<0.01	<0.01	<0.01	<0.001	<0.01	
Prep Wash																					
G1	Prep Blank		<0.001	0.002	<0.02	<0.01	<2	<0.001	<0.001	0.07	2.29	<0.02	0.07	<0.001	<0.01	<0.01	2.32	0.07	<0.001	0.62	6.65
G1	Prep Blank		<0.001	0.001	<0.02	<0.01	<2	<0.001	<0.001	0.08	2.33	<0.02	0.07	<0.001	<0.01	<0.01	2.36	0.07	<0.001	0.61	6.96



Acme Analytical Laboratories (Vancouver) Ltd.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: Selwyn Resources Ltd.

Suite 700 - 509 Richards Street

Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: December 06, 2010

Page: 1 of 1 **Part** 2

QUALITY CONTROL REPORT

WHI10000664.1

Method		7TD	7TD	7TD	7TD	G8SG
Analyte		Na	K	W	S	SG
Unit		%	%	%	%	
MDL		0.01	0.01	0.01	0.05	0
Pulp Duplicates						
REP 635411	QC	<0.01	0.14	<0.01	0.51	
635438	Drill Core	<0.01	4.47	<0.01	3.66	2.29
REP 635438	QC	<0.01	4.57	<0.01	3.65	
Core Reject Duplicates						
635411	Drill Core	<0.01	0.14	<0.01	0.51	2.39
DUP 635411	QC	<0.01	0.14	<0.01	0.52	2.40
Reference Materials						
STD OREAS131A	Standard	0.16	3.43	<0.01	4.72	
STD OREAS131A	Standard	0.16	3.48	<0.01	5.01	
STD R4T	Standard	0.93	1.19	<0.01	11.83	
STD R4T	Standard	0.93	1.19	<0.01	12.15	
STD SU-1B	Standard	1.69	0.61	<0.01	8.39	
STD SU-1B	Standard	1.72	0.63	<0.01	9.31	
STD R4T Expected		0.9	1.153	0.00016	12.9903	
STD OREAS131A Expected		0.1501	3.1584	0.0005	4.8	
STD SU-1B Expected		1.662	0.6	0.0007	8.76	
BLK	Blank	<0.01	<0.01	<0.01	<0.05	
BLK	Blank	<0.01	<0.01	<0.01	<0.05	
Prep Wash						
G1	Prep Blank	2.70	2.95	<0.01	<0.05	2.65
G1	Prep Blank	2.72	2.95	<0.01	<0.05	2.66



1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: Selwyn Resources Ltd.

Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Submitted By: Jason K. Dunning

Receiving Lab: Canada-Whitehorse

Received: November 23, 2010

Report Date: December 13, 2010

Page: 1 of 4

CERTIFICATE OF ANALYSIS

WHI10000663.1

CLIENT JOB INFORMATION

Project: Selwyn Project
Shipment ID:
P.O. Number: 1073
Number of Samples: 62

SAMPLE DISPOSAL

STOR-PLP Store After 90 days Invoice for Storage
STOR-RJT Store After 90 days Invoice for Storage

Acme does not accept responsibility for samples left at the laboratory after 90 days without prior written instructions for sample storage or return.

Invoice To: Selwyn Resources Ltd.
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6
Canada

CC:

SAMPLE PREPARATION AND ANALYTICAL PROCEDURES

Method Code	Number of Samples	Code Description	Test Wgt (g)	Report Status	Lab
R200-250	60	Crush split and pulverize 250g drill core to 200 mesh			WHI
7TD2	62	4 Acid digestion ICP-ES analysis.	0.5	Completed	VAN
G812	62	Specific Gravity on Pulp		Completed	VAN
7TD.1	4	4 Acid digestion ICP-ES analysis	0.1	Completed	VAN

ADDITIONAL COMMENTS



This report supersedes all previous preliminary and final reports with this file number dated prior to the date on this certificate. Signature indicates final approval; preliminary reports are unsigned and should be used for reference only.
All results are considered the confidential property of the client. Acme assumes the liabilities for actual cost of analysis only.
** asterisk indicates that an analytical result could not be provided due to unusually high levels of interference from other elements.



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: December 13, 2010

Page: 2 of 4 Part 1

CERTIFICATE OF ANALYSIS

WHI10000663.1

	Method Analyte Unit MDL	WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD
		Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg	Al
		kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%	%
		0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01	0.01
634501	Drill Core	1.15	0.001	0.006	<0.02	0.25	<2	0.008	<0.001	<0.01	1.15	<0.02	<0.01	<0.001	<0.01	<0.01	2.93	1.03	0.005	0.14	1.51
634502	Drill Core	2.93	<0.001	0.005	0.02	<0.01	<2	0.003	<0.001	0.05	2.48	<0.02	0.01	<0.001	<0.01	<0.01	25.78	0.17	0.001	0.11	0.35
634503	Drill Core	2.29	0.002	0.008	0.12	0.29	<2	0.009	<0.001	0.01	1.47	<0.02	<0.01	0.001	<0.01	<0.01	6.84	0.94	0.005	0.15	1.58
634504	Drill Core	1.86	0.003	0.003	0.02	0.32	<2	0.012	<0.001	<0.01	1.19	<0.02	<0.01	0.001	<0.01	<0.01	1.87	0.62	0.005	0.18	1.79
634505	Drill Core	2.21	0.003	0.012	3.09	10.60	4	0.008	<0.001	0.02	9.07	<0.02	<0.01	0.042	<0.01	<0.01	1.06	0.04	0.002	0.09	0.99
634506	Drill Core	1.25	0.002	0.010	3.20	10.30	4	0.006	<0.001	0.02	9.05	<0.02	<0.01	0.040	<0.01	<0.01	0.53	0.02	0.002	0.06	0.64
634507	Drill Core	3.40	<0.001	0.002	0.52	1.08	<2	0.003	<0.001	0.08	3.76	<0.02	0.01	0.004	<0.01	<0.01	28.90	0.02	<0.001	0.11	0.27
634508	Drill Core	2.14	0.003	0.007	1.53	10.18	3	0.008	<0.001	0.02	4.21	<0.02	<0.01	0.026	<0.01	<0.01	1.55	0.09	0.002	0.09	0.94
634509	Drill Core	2.48	<0.001	0.001	0.25	0.93	<2	0.002	<0.001	0.05	0.86	<0.02	0.02	0.003	<0.01	<0.01	31.45	0.02	<0.001	0.09	0.25
634510	Drill Core	1.18	0.002	0.002	0.17	1.32	<2	0.005	<0.001	0.02	1.47	<0.02	<0.01	0.004	<0.01	<0.01	6.60	0.07	0.002	0.07	0.63
634511	Drill Core	1.50	0.002	0.003	0.27	2.31	<2	0.005	<0.001	0.02	2.39	<0.02	<0.01	0.006	<0.01	<0.01	6.35	0.07	0.002	0.07	0.68
634512	Drill Core	1.73	0.002	0.002	0.06	0.98	<2	0.004	<0.001	<0.01	0.75	<0.02	<0.01	0.003	<0.01	<0.01	1.92	0.04	0.001	0.05	0.50
634513	Drill Core	2.58	0.007	0.003	0.34	1.02	<2	0.012	<0.001	<0.01	1.95	<0.02	<0.01	0.003	<0.01	<0.01	0.87	0.05	0.004	0.13	1.53
634514	Drill Core	2.50	0.005	0.020	3.20	18.67	4	0.010	<0.001	0.05	10.68	<0.02	<0.01	0.049	<0.01	<0.01	2.18	0.07	0.002	0.08	0.96
634515	Drill Core	1.78	<0.001	0.003	1.15	1.00	<2	0.001	<0.001	0.04	14.19	<0.02	0.01	0.003	<0.01	<0.01	21.55	0.06	<0.001	0.05	0.24
634516	Drill Core	0.57	0.003	0.015	4.91	16.00	4	0.008	<0.001	0.04	7.07	<0.02	<0.01	0.046	<0.01	<0.01	3.69	0.09	0.001	0.09	0.76
634517	Drill Core	1.34	<0.001	<0.001	0.03	0.02	<2	<0.001	<0.001	0.05	1.01	<0.02	0.02	<0.001	<0.01	<0.01	31.82	0.02	<0.001	0.07	0.12
634518	Drill Core	1.95	<0.001	0.002	0.81	4.34	<2	0.004	<0.001	0.03	1.83	<0.02	<0.01	0.013	<0.01	<0.01	12.94	0.06	0.002	0.07	0.56
634519	Drill Core	2.32	<0.001	0.002	0.75	5.26	<2	0.006	<0.001	0.02	2.23	<0.02	<0.01	0.014	<0.01	<0.01	1.90	0.06	0.002	0.08	0.66
634520	Rock	0.29	<0.001	<0.001	<0.02	0.02	<2	<0.001	<0.001	0.02	0.10	<0.02	<0.01	<0.001	<0.01	<0.01	21.52	0.03	<0.001	11.24	0.08
634521	Drill Core	2.13	0.001	0.003	0.82	5.73	<2	0.006	<0.001	0.03	2.48	<0.02	<0.01	0.015	<0.01	<0.01	3.11	0.07	0.002	0.09	0.79
634522	Drill Core	0.94	<0.001	0.003	1.40	7.42	<2	0.005	<0.001	0.02	2.59	<0.02	<0.01	0.020	<0.01	<0.01	2.54	0.07	0.002	0.10	0.78
634523	Drill Core	1.72	0.002	0.001	0.89	0.77	<2	0.002	<0.001	0.04	1.22	<0.02	0.02	0.002	<0.01	<0.01	31.73	0.06	<0.001	0.11	0.47
634524	Drill Core	1.93	0.002	0.002	0.36	2.45	<2	0.003	<0.001	0.04	1.78	<0.02	0.02	0.007	<0.01	<0.01	29.33	0.03	<0.001	0.08	0.36
634525	Drill Core	0.57	<0.001	0.003	3.64	18.49	4	0.002	<0.001	0.04	1.75	<0.02	<0.01	0.073	<0.01	<0.01	15.01	0.03	<0.001	0.04	0.17
634526	Drill Core	2.73	<0.001	0.003	2.27	5.41	<2	0.005	<0.001	0.02	2.98	<0.02	<0.01	0.017	<0.01	<0.01	5.47	0.06	0.001	0.09	0.69
634527	Drill Core	0.64	<0.001	0.006	9.99	30.44	8	0.004	<0.001	0.01	2.89	<0.02	<0.01	0.082	<0.01	<0.01	1.06	0.04	0.001	0.04	0.46
634528	Drill Core	1.35	<0.001	0.004	>10	29.72	8	0.003	<0.001	<0.01	2.13	<0.02	<0.01	0.112	<0.01	<0.01	0.75	0.08	0.002	0.06	0.56
634529	Drill Core	1.18	<0.001	0.001	>10	13.64	3	0.003	<0.001	<0.01	1.46	<0.02	<0.01	0.059	<0.01	<0.01	0.27	0.05	0.001	0.05	0.47
634530	Rock Pulp	0.06	<0.001	0.495	1.45	4.40	31	<0.001	0.001	0.68	5.40	<0.02	0.01	0.027	<0.01	<0.01	4.31	0.05	0.003	1.54	4.62



Acme Analytical Laboratories (Vancouver) Ltd.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client:

Selwyn Resources Ltd.

Suite 700 - 509 Richards Street

Vancouver BC V6B 2Z6 Canada

Project:

Selwyn Project

Report Date:

December 13, 2010

Page:

2 of 4

Part 2

CERTIFICATE OF ANALYSIS

WHI10000663.1

	Method Analyte Unit MDL	7TD	7TD	7TD	7TD	G8SG	7TD.1
		Na	K	W	S	SG	Pb
		%	%	%	%		%
		0.01	0.01	0.01	0.05	0	0.02
634501	Drill Core	<0.01	0.77	<0.01	1.23	2.40	
634502	Drill Core	<0.01	0.19	<0.01	3.17	2.64	
634503	Drill Core	<0.01	0.81	<0.01	1.68	2.39	
634504	Drill Core	<0.01	1.00	<0.01	1.32	2.27	
634505	Drill Core	<0.01	0.60	<0.01	15.64	2.84	
634506	Drill Core	<0.01	0.36	<0.01	15.49	2.86	
634507	Drill Core	<0.01	0.14	<0.01	5.36	2.62	
634508	Drill Core	<0.01	0.57	<0.01	9.49	2.62	
634509	Drill Core	<0.01	0.14	<0.01	1.69	2.61	
634510	Drill Core	<0.01	0.36	<0.01	2.18	2.43	
634511	Drill Core	<0.01	0.41	<0.01	3.74	2.51	
634512	Drill Core	<0.01	0.29	<0.01	1.06	2.43	
634513	Drill Core	<0.01	1.02	<0.01	2.51	2.27	
634514	Drill Core	<0.01	0.64	<0.01	21.71	2.99	
634515	Drill Core	<0.01	0.14	<0.01	18.19	2.99	
634516	Drill Core	0.01	0.42	<0.01	16.37	2.76	
634517	Drill Core	<0.01	0.05	<0.01	1.40	2.67	
634518	Drill Core	<0.01	0.32	<0.01	4.49	2.60	
634519	Drill Core	<0.01	0.39	<0.01	5.00	2.51	
634520	Rock	<0.01	0.01	<0.01	0.15	2.68	
634521	Drill Core	<0.01	0.46	<0.01	5.50	2.50	
634522	Drill Core	<0.01	0.48	<0.01	6.68	2.57	
634523	Drill Core	<0.01	0.24	<0.01	2.17	2.58	
634524	Drill Core	<0.01	0.18	<0.01	3.72	2.60	
634525	Drill Core	<0.01	0.10	<0.01	11.43	2.91	
634526	Drill Core	<0.01	0.39	<0.01	6.20	2.61	
634527	Drill Core	<0.01	0.27	<0.01	19.19	3.30	
634528	Drill Core	<0.01	0.30	<0.01	18.54	3.27	15.06
634529	Drill Core	<0.01	0.24	<0.01	9.33	2.95	10.41
634530	Rock Pulp	0.09	3.26	<0.01	5.02	N.A.	



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: December 13, 2010

Page: 3 of 4 Part 1

CERTIFICATE OF ANALYSIS

WHI10000663.1

	Method Analyte Unit MDL	WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD
		Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg	Al
		kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%	%
		0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01	0.01
634531	Drill Core	1.55	0.002	0.004	>10	18.49	5	0.008	0.002	0.01	2.55	<0.02	<0.01	0.061	<0.01	<0.01	1.78	0.07	0.003	0.11	1.08
634532	Drill Core	1.22	<0.001	0.002	3.96	15.77	<2	0.002	<0.001	<0.01	1.25	<0.02	<0.01	0.039	<0.01	<0.01	0.40	0.03	<0.001	0.03	0.27
634533	Drill Core	1.34	<0.001	0.003	6.60	21.49	3	0.002	<0.001	<0.01	1.70	<0.02	<0.01	0.057	<0.01	<0.01	0.55	0.03	<0.001	0.01	0.14
634534	Drill Core	1.13	<0.001	0.003	4.68	24.07	5	0.003	<0.001	0.01	2.30	<0.02	<0.01	0.062	<0.01	<0.01	1.21	0.02	<0.001	0.02	0.18
634535	Drill Core	1.17	0.001	0.008	6.11	39.11	11	0.005	<0.001	0.01	3.77	<0.02	<0.01	0.103	<0.01	<0.01	2.34	0.05	0.001	0.04	0.34
634536	Drill Core	2.22	0.001	0.002	2.72	3.60	<2	0.004	<0.001	0.02	1.73	<0.02	<0.01	0.009	<0.01	<0.01	11.39	0.02	0.001	0.07	0.46
634537	Drill Core	1.69	<0.001	0.003	>10	27.49	4	0.001	<0.001	<0.01	1.27	<0.02	<0.01	0.079	<0.01	<0.01	1.39	0.03	<0.001	0.02	0.16
634538	Drill Core	0.28	0.002	0.005	2.04	9.28	3	0.006	<0.001	0.01	3.01	<0.02	<0.01	0.026	<0.01	<0.01	0.69	0.06	0.002	0.07	0.67
634539	Drill Core	1.06	<0.001	0.003	6.90	26.32	3	0.002	<0.001	0.01	1.67	<0.02	<0.01	0.076	<0.01	<0.01	1.05	0.03	<0.001	0.02	0.22
634540	Drill Core	0.33	<0.001	0.007	4.13	33.99	8	0.004	<0.001	0.02	2.58	<0.02	<0.01	0.095	<0.01	<0.01	0.44	0.04	<0.001	0.03	0.25
634541	Drill Core	0.35	<0.001	0.006	4.32	33.12	7	0.003	<0.001	0.02	2.39	<0.02	<0.01	0.094	<0.01	<0.01	0.41	0.04	<0.001	0.03	0.23
634542	Drill Core	2.62	0.003	0.004	2.69	7.38	<2	0.008	<0.001	0.02	2.60	<0.02	<0.01	0.020	<0.01	<0.01	10.77	0.08	0.002	0.12	1.00
634543	Drill Core	1.37	<0.001	0.004	3.58	16.98	<2	0.003	<0.001	0.02	1.80	<0.02	<0.01	0.051	<0.01	<0.01	5.40	0.03	<0.001	0.04	0.27
634544	Drill Core	0.80	<0.001	0.005	4.60	22.43	<2	0.003	<0.001	0.01	2.06	<0.02	<0.01	0.071	<0.01	<0.01	1.43	0.03	<0.001	0.03	0.27
634545	Drill Core	1.84	0.002	0.003	0.84	3.55	<2	0.006	<0.001	0.03	1.49	<0.02	<0.01	0.011	<0.01	<0.01	17.58	0.11	0.002	0.14	0.87
634546	Drill Core	3.58	<0.001	0.003	0.02	0.04	<2	0.004	<0.001	0.05	0.81	<0.02	0.02	<0.001	<0.01	<0.01	28.09	0.05	0.001	0.12	0.50
634547	Drill Core	3.46	<0.001	0.003	0.03	0.02	<2	0.004	<0.001	<0.01	1.13	<0.02	<0.01	<0.001	<0.01	<0.01	2.10	0.04	0.001	0.05	0.40
634548	Drill Core	2.23	0.002	0.006	0.17	0.91	<2	0.008	<0.001	0.03	2.05	<0.02	<0.01	0.002	<0.01	<0.01	13.46	0.17	0.003	0.11	0.77
634549	Drill Core	2.30	0.001	0.004	0.10	0.29	<2	0.005	<0.001	0.03	1.28	<0.02	<0.01	<0.001	<0.01	<0.01	13.88	0.15	0.001	0.08	0.32
634550	Rock	0.36	<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	0.02	0.13	<0.02	0.01	<0.001	<0.01	<0.01	21.88	0.04	<0.001	11.56	0.05
634551	Drill Core	2.04	0.004	0.013	0.37	0.35	<2	0.008	<0.001	0.02	1.98	<0.02	0.01	0.001	<0.01	<0.01	16.12	1.30	0.004	0.11	0.49
634552	Drill Core	2.31	0.004	0.011	0.13	0.54	<2	0.008	<0.001	0.03	0.52	<0.02	0.02	0.002	<0.01	<0.01	22.68	0.67	0.003	0.13	0.61
634553	Drill Core	2.44	0.002	0.007	0.03	0.10	<2	0.006	<0.001	0.02	1.22	<0.02	<0.01	<0.001	<0.01	<0.01	15.28	0.45	0.001	0.08	0.38
634554	Drill Core	2.21	0.004	0.019	0.39	0.92	<2	0.009	<0.001	0.02	3.52	<0.02	<0.01	0.002	<0.01	<0.01	12.77	0.30	0.003	0.09	0.63
634555	Drill Core	1.83	0.007	0.019	0.18	0.84	3	0.015	<0.001	0.02	3.64	<0.02	<0.01	0.003	<0.01	<0.01	11.32	0.27	0.005	0.13	1.05
634556	Drill Core	1.79	0.004	0.014	0.14	0.63	<2	0.022	<0.001	0.01	1.88	<0.02	0.01	0.002	<0.01	<0.01	8.09	1.87	0.011	0.23	1.63
634557	Drill Core	1.18	<0.001	0.005	0.14	0.13	<2	0.008	<0.001	0.03	3.28	<0.02	0.01	<0.001	<0.01	<0.01	18.87	0.73	0.006	0.33	2.66
634558	Drill Core	2.18	<0.001	0.002	<0.02	<0.01	<2	0.002	<0.001	0.04	2.69	<0.02	0.01	<0.001	<0.01	<0.01	21.66	0.05	0.003	0.41	2.84
634559	Drill Core	1.84	<0.001	0.002	<0.02	<0.01	<2	0.003	<0.001	0.04	2.33	<0.02	0.01	<0.001	<0.01	<0.01	21.61	0.03	0.003	0.40	2.50
634560	Rock Pulp	0.06	0.001	0.659	5.95	6.74	68	0.001	<0.001	0.09	4.99	<0.02	0.02	0.019	0.02	<0.01	1.36	0.02	<0.001	0.25	5.23



Acme Analytical Laboratories (Vancouver) Ltd.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client:

Selwyn Resources Ltd.

Suite 700 - 509 Richards Street

Vancouver BC V6B 2Z6 Canada

Project:

Selwyn Project

Report Date:

December 13, 2010

Page:

3 of 4

Part 2

CERTIFICATE OF ANALYSIS

WHI10000663.1

	Method Analyte Unit MDL	7TD	7TD	7TD	7TD	G8SG	7TD.1
		Na	K	W	S	SG	Pb
		%	%	%	%		%
		0.01	0.01	0.01	0.05	0	0.02
634531	Drill Core	<0.01	0.59	<0.01	12.87	2.96	11.91
634532	Drill Core	<0.01	0.15	<0.01	9.34	2.77	
634533	Drill Core	<0.01	0.07	<0.01	12.82	3.01	
634534	Drill Core	<0.01	0.09	<0.01	14.38	2.95	
634535	Drill Core	<0.01	0.19	<0.01	23.34	3.26	
634536	Drill Core	<0.01	0.25	<0.01	3.89	2.57	
634537	Drill Core	<0.01	0.08	<0.01	15.17	3.17	10.61
634538	Drill Core	<0.01	0.36	<0.01	7.92	2.65	
634539	Drill Core	<0.01	0.11	<0.01	14.92	3.13	
634540	Drill Core	<0.01	0.12	<0.01	19.23	3.20	
634541	Drill Core	<0.01	0.11	<0.01	18.72	3.16	
634542	Drill Core	<0.01	0.59	<0.01	6.71	2.60	
634543	Drill Core	<0.01	0.14	<0.01	10.27	2.84	
634544	Drill Core	<0.01	0.14	<0.01	13.41	3.10	
634545	Drill Core	<0.01	0.50	<0.01	3.26	2.49	
634546	Drill Core	<0.01	0.30	<0.01	0.94	2.54	
634547	Drill Core	<0.01	0.22	<0.01	0.82	2.55	
634548	Drill Core	<0.01	0.49	<0.01	2.65	2.45	
634549	Drill Core	<0.01	0.20	<0.01	1.32	2.47	
634550	Rock	<0.01	0.01	<0.01	<0.05	2.76	
634551	Drill Core	<0.01	0.29	<0.01	2.23	2.51	
634552	Drill Core	<0.01	0.36	<0.01	0.71	2.45	
634553	Drill Core	<0.01	0.22	<0.01	1.31	2.45	
634554	Drill Core	<0.01	0.37	<0.01	4.26	2.50	
634555	Drill Core	<0.01	0.65	<0.01	4.49	2.34	
634556	Drill Core	<0.01	0.91	<0.01	2.18	2.27	
634557	Drill Core	<0.01	1.88	<0.01	3.66	2.55	
634558	Drill Core	<0.01	1.87	<0.01	2.86	2.74	
634559	Drill Core	<0.01	1.56	<0.01	2.79	2.72	
634560	Rock Pulp	2.29	1.36	<0.01	5.78	N.A.	



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: December 13, 2010

Page: 4 of 4 **Part** 1

CERTIFICATE OF ANALYSIS

WHI10000663.1

	Method Analyte Unit MDL	WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD
		Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg	Al
		kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%	%
		0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01	0.01
634561	Drill Core	1.48	0.002	0.002	<0.02	<0.01	<2	0.005	<0.001	0.04	1.60	<0.02	0.02	<0.001	<0.01	<0.01	24.99	0.29	0.003	0.33	2.46
634562	Drill Core	0.88	0.007	0.009	<0.02	<0.01	<2	0.021	<0.001	0.01	3.93	<0.02	0.02	<0.001	<0.01	<0.01	14.12	4.71	0.014	0.29	2.67



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: December 13, 2010

Page: 4 of 4 **Part** 2

CERTIFICATE OF ANALYSIS

WHI10000663.1

	Method Analyte Unit MDL	7TD	7TD	7TD	7TD	G8SG	7TD.1
		Na	K	W	S	SG	Pb
		%	%	%	%		%
		0.01	0.01	0.01	0.05	0	0.02
634561	Drill Core	<0.01	1.69	<0.01	1.79	2.57	
634562	Drill Core	<0.01	1.71	<0.01	4.57	2.26	



Acme Analytical Laboratories (Vancouver) Ltd.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: **Selwyn Resources Ltd.**

Suite 700 - 509 Richards Street

Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: December 13, 2010

Page: 1 of 2 Part 1

QUALITY CONTROL REPORT

WHI10000663.1

	Method Analyte Unit MDL	WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	
		Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg	Al
		kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%	%
		0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01	0.01
Pulp Duplicates																					
634503	Drill Core	2.29	0.002	0.008	0.12	0.29	<2	0.009	<0.001	0.01	1.47	<0.02	<0.01	0.001	<0.01	<0.01	6.84	0.94	0.005	0.15	1.58
REP 634503	QC		0.002	0.008	0.12	0.29	<2	0.009	<0.001	0.02	1.52	<0.02	<0.01	0.001	<0.01	<0.01	6.81	0.93	0.005	0.15	1.57
634531	Drill Core	1.55	0.002	0.004	>10	18.49	5	0.008	0.002	0.01	2.55	<0.02	<0.01	0.061	<0.01	<0.01	1.78	0.07	0.003	0.11	1.08
REP 634531	QC																				
634545	Drill Core	1.84	0.002	0.003	0.84	3.55	<2	0.006	<0.001	0.03	1.49	<0.02	<0.01	0.011	<0.01	<0.01	17.58	0.11	0.002	0.14	0.87
REP 634545	QC		0.001	0.003	0.82	3.50	<2	0.006	<0.001	0.03	1.44	<0.02	<0.01	0.011	<0.01	<0.01	17.80	0.10	0.002	0.14	0.88
634561	Drill Core	1.48	0.002	0.002	<0.02	<0.01	<2	0.005	<0.001	0.04	1.60	<0.02	0.02	<0.001	<0.01	<0.01	24.99	0.29	0.003	0.33	2.46
REP 634561	QC		0.001	0.002	<0.02	<0.01	<2	0.004	<0.001	0.04	1.53	<0.02	0.02	<0.001	<0.01	<0.01	24.04	0.27	0.003	0.32	2.37
Core Reject Duplicates																					
634515	Drill Core	1.78	<0.001	0.003	1.15	1.00	<2	0.001	<0.001	0.04	14.19	<0.02	0.01	0.003	<0.01	<0.01	21.55	0.06	<0.001	0.05	0.24
DUP 634515	QC		<0.001	0.003	1.23	1.07	<2	0.001	<0.001	0.04	15.44	<0.02	0.01	0.003	<0.01	<0.01	21.70	0.06	<0.001	0.06	0.26
634550	Rock	0.36	<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	0.02	0.13	<0.02	0.01	<0.001	<0.01	<0.01	21.88	0.04	<0.001	11.56	0.05
DUP 634550	QC		<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	0.02	0.13	<0.02	<0.01	<0.001	<0.01	<0.01	21.76	0.03	<0.001	11.41	0.05
Reference Materials																					
STD CCU-1C	Standard																				
STD CZN-3	Standard																				
STD OREAS131A	Standard		<0.001	0.032	1.72	2.90	31	0.002	0.002	0.17	5.88	<0.02	<0.01	0.008	<0.01	<0.01	5.39	0.05	0.002	3.19	4.70
STD OREAS131A	Standard		<0.001	0.032	1.75	2.88	31	0.003	0.002	0.17	5.92	<0.02	<0.01	0.008	<0.01	<0.01	5.31	0.06	0.003	3.18	4.65
STD OREAS131A	Standard		<0.001	0.032	1.69	2.91	31	0.003	0.002	0.18	5.87	<0.02	<0.01	0.008	<0.01	<0.01	5.45	0.06	0.003	3.11	4.60
STD PTC-1A	Standard																				
STD R4T	Standard		0.066	0.521	1.59	3.50	89	0.361	0.043	0.09	24.74	<0.02	0.02	0.019	0.02	<0.01	2.25	0.05	0.019	1.47	4.11
STD R4T	Standard		0.064	0.511	1.55	3.44	85	0.354	0.041	0.09	24.50	<0.02	0.02	0.018	0.02	<0.01	2.19	0.04	0.019	1.42	3.96
STD R4T	Standard		0.064	0.512	1.52	3.46	86	0.352	0.041	0.09	24.74	<0.02	0.02	0.019	0.02	<0.01	2.19	0.05	0.019	1.39	3.75
STD SARM 71	Standard																				
STD SU-1B	Standard		<0.001	1.204	<0.02	0.03	6	2.010	0.068	0.07	25.68	<0.02	0.03	<0.001	<0.01	<0.01	2.26	0.06	0.031	1.84	4.52
STD SU-1B	Standard		<0.001	1.182	<0.02	0.03	4	2.001	0.067	0.07	25.76	<0.02	0.03	<0.001	<0.01	<0.01	2.24	0.06	0.031	1.80	4.41
STD SU-1B	Standard		<0.001	1.211	<0.02	0.03	7	1.985	0.069	0.07	26.26	<0.02	0.03	<0.001	<0.01	<0.01	2.24	0.08	0.032	1.79	4.38
STD R4T Expected			0.062	0.502	1.518	3.376	86	0.339	0.039	0.086	24.07	0.0087	0.0185	0.018	0.0138	0.0018	2.166	0.045	0.018	1.384	3.897



Acme Analytical Laboratories (Vancouver) Ltd.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: Selwyn Resources Ltd.

Suite 700 - 509 Richards Street

Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: December 13, 2010

Page: 1 of 2 **Part** 2

QUALITY CONTROL REPORT

WHI10000663.1

Method		7TD	7TD	7TD	7TD	G8SG	7TD.1
Analyte		Na	K	W	S	SG	Pb
Unit		%	%	%	%		%
MDL		0.01	0.01	0.01	0.05	0	0.02
Pulp Duplicates							
634503	Drill Core	<0.01	0.81	<0.01	1.68	2.39	
REP 634503	QC	<0.01	0.91	<0.01	1.68		
634531	Drill Core	<0.01	0.59	<0.01	12.87	2.96	11.91
REP 634531	QC						11.95
634545	Drill Core	<0.01	0.50	<0.01	3.26	2.49	
REP 634545	QC	<0.01	0.49	<0.01	3.18		
634561	Drill Core	<0.01	1.69	<0.01	1.79	2.57	
REP 634561	QC	<0.01	1.64	<0.01	1.71		
Core Reject Duplicates							
634515	Drill Core	<0.01	0.14	<0.01	18.19	2.99	
DUP 634515	QC	<0.01	0.15	<0.01	18.91	3.03	
634550	Rock	<0.01	0.01	<0.01	<0.05	2.76	
DUP 634550	QC	<0.01	0.02	<0.01	<0.05	2.72	
Reference Materials							
STD CCU-1C	Standard						0.41
STD CZN-3	Standard						0.13
STD OREAS131A	Standard	0.15	3.42	<0.01	4.69		
STD OREAS131A	Standard	0.15	3.38	<0.01	4.96		
STD OREAS131A	Standard	0.15	3.38	<0.01	4.98		
STD PTC-1A	Standard						0.05
STD R4T	Standard	0.93	1.20	<0.01	12.55		
STD R4T	Standard	0.92	1.17	<0.01	13.10		
STD R4T	Standard	0.94	1.17	<0.01	13.27		
STD SARM 71	Standard						<0.02
STD SU-1B	Standard	1.71	0.62	<0.01	8.91		
STD SU-1B	Standard	1.71	0.61	<0.01	9.34		
STD SU-1B	Standard	1.72	0.63	<0.01	9.62		
STD R4T Expected		0.9	1.153	0.00016	12.9903		



Acme Analytical Laboratories (Vancouver) Ltd.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: **Selwyn Resources Ltd.**

Suite 700 - 509 Richards Street

Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: December 13, 2010

Page: 2 of 2 Part 1

QUALITY CONTROL REPORT

WHI10000663.1

		WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	
		Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg	Al
		kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%	%
		0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01	0.01
STD OREAS131A Expected			0.001	0.0322	1.72	2.83	30.9	0.0027	0.0023	0.1722	5.8166	0.0082	0.0028	0.0081	0.0047	0.001	5.286	0.0536	0.0025	3.1182	4.6057
STD SU-1B Expected			0.0004	1.185	0.0058	0.0235	6.4	1.97	0.0672	0.0703	25.54	0.00025	0.03	0.0003	0.00002	0.0003	2.21	0.06	0.032	1.79	4.39
STD CZN-3 Expected																					
STD CCU-1C Expected																					
STD PTC-1A Expected																					
BLK	Blank		<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	<0.01	<0.01	<0.02	<0.01	<0.001	<0.01	<0.01	<0.01	<0.01	<0.001	<0.01	<0.01
BLK	Blank		<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	<0.01	<0.01	<0.02	<0.01	<0.001	<0.01	<0.01	<0.01	<0.01	<0.001	<0.01	<0.01
BLK	Blank																				
Prep Wash																					
G1	Prep Blank		<0.001	<0.001	<0.02	0.02	<2	<0.001	<0.001	0.08	2.38	<0.02	0.07	<0.001	<0.01	<0.01	2.29	0.08	<0.001	0.60	7.49
G1	Prep Blank		<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	0.07	2.29	<0.02	0.07	<0.001	<0.01	<0.01	2.31	0.07	<0.001	0.58	7.58



Acme Analytical Laboratories (Vancouver) Ltd.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: **Selwyn Resources Ltd.**

Suite 700 - 509 Richards Street

Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: December 13, 2010

Page: 2 of 2 **Part** 2

QUALITY CONTROL REPORT

WHI10000663.1

		7TD Na %	7TD K %	7TD W %	7TD S %	G8SG SG 0	7TD.1 Pb %
		0.01	0.01	0.01	0.05		0.02
STD OREAS131A Expected		0.1501	3.1584	0.0005	4.8		
STD SU-1B Expected		1.662	0.6	0.0007	8.76		
STD CZN-3 Expected							0.113
STD CCU-1C Expected							0.34
STD PTC-1A Expected							0.05
BLK	Blank	<0.01	<0.01	<0.01	<0.05		
BLK	Blank	<0.01	<0.01	<0.01	<0.05		
BLK	Blank						<0.02
Prep Wash							
G1	Prep Blank	2.69	2.12	<0.01	0.06	2.68	
G1	Prep Blank	2.71	1.27	<0.01	<0.05	2.71	



1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**

Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Submitted By: Jason K. Dunning

Receiving Lab: Canada-Whitehorse

Received: November 22, 2010

Report Date: December 13, 2010

Page: 1 of 4

CERTIFICATE OF ANALYSIS

WHI10000659.1

CLIENT JOB INFORMATION

Project: Selwyn Project
Shipment ID:
P.O. Number: 1057
Number of Samples: 81

SAMPLE DISPOSAL

STOR-PLP Store After 90 days Invoice for Storage
STOR-RJT Store After 90 days Invoice for Storage

Acme does not accept responsibility for samples left at the laboratory after 90 days without prior written instructions for sample storage or return.

Invoice To: Selwyn Resources Ltd.
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6
Canada

CC:

SAMPLE PREPARATION AND ANALYTICAL PROCEDURES

Method Code	Number of Samples	Code Description	Test Wgt (g)	Report Status	Lab
R200-250	79	Crush split and pulverize 250g drill core to 200 mesh			WHI
7TD2	81	4 Acid digestion ICP-ES analysis.	0.5	Completed	VAN
G812	81	Specific Gravity on Pulp		Completed	VAN
7TD.1	2	4 Acid digestion ICP-ES analysis	0.1	Completed	VAN

ADDITIONAL COMMENTS



This report supersedes all previous preliminary and final reports with this file number dated prior to the date on this certificate. Signature indicates final approval; preliminary reports are unsigned and should be used for reference only.
All results are considered the confidential property of the client. Acme assumes the liabilities for actual cost of analysis only.
** asterisk indicates that an analytical result could not be provided due to unusually high levels of interference from other elements.



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: December 13, 2010

Page: 2 of 4 Part 1

CERTIFICATE OF ANALYSIS

WHI10000659.1

	Method Analyte Unit MDL	WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD
		Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg	Al
		kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%	%
		0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01	0.01
633001	Drill Core	1.03	<0.001	0.009	0.34	7.40	6	0.003	<0.001	0.02	3.30	<0.02	0.01	0.017	<0.01	<0.01	13.43	0.02	0.002	0.13	0.56
633002	Drill Core	0.83	<0.001	0.014	0.25	5.84	5	0.005	<0.001	0.01	4.36	<0.02	<0.01	0.013	<0.01	<0.01	7.22	0.47	0.003	0.21	1.05
633003	Drill Core	1.04	<0.001	0.007	0.17	1.67	3	0.012	<0.001	0.01	1.82	<0.02	0.01	0.005	<0.01	<0.01	8.52	1.65	0.009	0.53	3.14
633004	Drill Core	1.28	0.001	0.013	0.64	11.53	7	0.004	<0.001	0.02	2.73	<0.02	0.01	0.026	<0.01	<0.01	13.78	0.01	0.001	0.15	0.56
633005	Drill Core	1.06	0.001	0.015	2.96	15.70	8	0.002	<0.001	0.02	3.20	<0.02	0.01	0.039	<0.01	<0.01	7.43	<0.01	<0.001	0.10	0.38
633006	Drill Core	1.21	<0.001	0.015	3.92	10.57	9	0.004	<0.001	0.02	6.17	<0.02	0.01	0.031	<0.01	<0.01	8.98	0.02	0.002	0.16	0.63
633007	Drill Core	1.94	0.002	0.003	<0.02	0.30	<2	0.010	<0.001	<0.01	0.84	<0.02	<0.01	0.001	<0.01	<0.01	2.54	1.14	0.004	0.14	1.54
633008	Drill Core	2.30	0.003	0.006	0.20	0.61	2	0.011	<0.001	<0.01	1.42	<0.02	<0.01	0.002	<0.01	<0.01	1.36	0.54	0.004	0.13	1.54
633009	Drill Core	1.81	0.003	0.002	0.41	0.32	<2	0.009	<0.001	<0.01	0.84	<0.02	<0.01	0.001	<0.01	<0.01	0.81	0.06	0.002	0.11	1.25
633010	Drill Core	0.69	0.010	0.012	0.90	5.36	4	0.017	<0.001	0.02	6.65	<0.02	<0.01	0.020	<0.01	<0.01	2.19	0.09	0.004	0.18	2.44
633011	Drill Core	0.63	0.010	0.013	1.08	6.52	5	0.017	0.001	0.02	6.60	<0.02	<0.01	0.024	<0.01	<0.01	1.17	0.09	0.004	0.18	2.48
633012	Drill Core	1.23	0.004	0.013	2.61	10.98	5	0.010	<0.001	0.02	6.29	<0.02	<0.01	0.035	<0.01	<0.01	0.47	0.05	0.002	0.09	1.15
633013	Drill Core	1.52	0.003	0.010	2.59	12.58	4	0.007	<0.001	0.01	6.35	<0.02	<0.01	0.045	<0.01	<0.01	0.80	0.03	0.001	0.06	0.74
633014	Drill Core	1.71	<0.001	0.001	0.51	0.50	<2	0.002	<0.001	0.09	2.38	<0.02	0.02	0.002	<0.01	<0.01	34.63	0.02	<0.001	0.11	0.10
633015	Drill Core	1.26	0.001	0.003	1.64	1.94	<2	0.003	<0.001	0.04	3.20	<0.02	<0.01	0.006	<0.01	<0.01	19.12	0.03	<0.001	0.07	0.32
633016	Drill Core	1.04	0.004	0.007	1.76	5.40	2	0.010	<0.001	0.02	5.84	<0.02	<0.01	0.013	<0.01	<0.01	1.40	0.05	0.002	0.10	1.13
633017	Drill Core	1.22	<0.001	0.001	1.03	1.45	<2	<0.001	<0.001	0.13	2.19	<0.02	0.02	0.004	<0.01	<0.01	33.23	0.03	<0.001	0.17	0.06
633018	Drill Core	0.72	0.007	0.010	2.53	11.80	3	0.012	<0.001	0.02	6.10	<0.02	<0.01	0.034	<0.01	<0.01	1.91	0.10	0.003	0.12	1.63
633019	Drill Core	2.04	<0.001	0.003	5.68	18.58	<2	0.002	<0.001	<0.01	0.72	<0.02	<0.01	0.090	<0.01	<0.01	1.90	0.06	<0.001	0.03	0.30
633020	Rock	0.26	<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	0.02	0.16	<0.02	0.01	<0.001	<0.01	<0.01	22.26	0.03	<0.001	11.20	0.09
633021	Drill Core	0.74	<0.001	0.003	4.99	15.14	3	0.002	<0.001	<0.01	0.87	<0.02	<0.01	0.069	<0.01	<0.01	0.50	0.02	<0.001	0.05	0.25
633022	Drill Core	0.80	0.003	0.007	4.32	3.55	3	0.006	<0.001	0.02	17.44	<0.02	<0.01	0.015	<0.01	<0.01	4.95	0.13	0.002	0.07	0.82
633023	Drill Core	0.94	<0.001	<0.001	0.07	0.05	<2	<0.001	<0.001	0.06	0.27	<0.02	0.02	<0.001	<0.01	<0.01	36.66	0.01	<0.001	0.08	0.04
633024	Drill Core	0.69	0.004	0.003	>10	4.09	3	0.008	<0.001	0.03	1.46	<0.02	<0.01	0.015	<0.01	<0.01	9.68	0.09	0.002	0.13	1.23
633025	Drill Core	0.83	<0.001	0.003	>10	9.30	6	<0.001	<0.001	0.01	0.44	<0.02	<0.01	0.035	<0.01	<0.01	4.58	0.02	<0.001	0.03	0.24
633026	Drill Core	2.39	<0.001	0.002	1.82	0.81	<2	0.002	<0.001	0.04	1.95	<0.02	0.01	0.003	<0.01	<0.01	22.12	0.03	<0.001	0.09	0.22
633027	Drill Core	1.25	0.002	0.002	0.48	2.04	<2	0.003	<0.001	<0.01	0.73	<0.02	<0.01	0.008	<0.01	<0.01	1.39	0.04	<0.001	0.04	0.41
633028	Drill Core	2.24	0.004	0.002	0.08	0.79	<2	0.009	<0.001	<0.01	0.92	<0.02	<0.01	0.002	<0.01	<0.01	3.03	0.05	0.002	0.09	1.01
633029	Drill Core	0.73	0.003	0.001	0.04	0.31	<2	0.007	<0.001	0.03	0.94	<0.02	0.01	<0.001	<0.01	<0.01	22.39	0.03	0.001	0.09	0.64
633030	Rock Pulp	0.06	0.002	0.856	0.97	1.29	221	0.001	0.002	0.23	2.81	<0.02	0.01	0.009	0.03	<0.01	1.95	0.01	0.003	0.13	1.26



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: December 13, 2010

Page: 2 of 4 **Part** 2

CERTIFICATE OF ANALYSIS

WHI10000659.1

	Method Analyte Unit MDL	7TD	7TD	7TD	7TD	G8SG	7TD.1
		Na	K	W	S	SG	Pb
		%	%	%	%		%
		0.01	0.01	0.01	0.05	0	0.02
633001	Drill Core	<0.01	0.31	<0.01	7.36	2.67	
633002	Drill Core	<0.01	0.74	<0.01	7.59	2.64	
633003	Drill Core	0.01	2.07	<0.01	2.69	2.24	
633004	Drill Core	<0.01	0.34	<0.01	8.85	2.72	
633005	Drill Core	<0.01	0.22	<0.01	11.55	2.85	
633006	Drill Core	<0.01	0.37	<0.01	12.69	2.78	
633007	Drill Core	<0.01	0.81	<0.01	0.95	2.27	
633008	Drill Core	<0.01	0.84	<0.01	1.73	2.29	
633009	Drill Core	<0.01	0.69	<0.01	1.02	2.29	
633010	Drill Core	<0.01	1.46	<0.01	10.64	2.34	
633011	Drill Core	<0.01	1.46	<0.01	11.27	2.32	
633012	Drill Core	<0.01	0.62	<0.01	13.07	2.47	
633013	Drill Core	<0.01	0.41	<0.01	13.64	2.66	
633014	Drill Core	<0.01	0.09	<0.01	3.09	2.51	
633015	Drill Core	<0.01	0.18	<0.01	4.80	2.54	
633016	Drill Core	<0.01	0.58	<0.01	9.52	2.46	
633017	Drill Core	<0.01	0.06	<0.01	3.38	2.63	
633018	Drill Core	<0.01	0.94	<0.01	12.98	2.52	
633019	Drill Core	<0.01	0.15	<0.01	10.60	2.82	
633020	Rock	0.01	0.03	<0.01	<0.05	2.52	
633021	Drill Core	<0.01	0.12	<0.01	8.78	2.79	
633022	Drill Core	<0.01	0.52	<0.01	22.15	3.00	
633023	Drill Core	<0.01	0.07	<0.01	0.39	2.47	
633024	Drill Core	<0.01	0.68	<0.01	5.08	2.48	10.45
633025	Drill Core	<0.01	0.15	<0.01	7.88	3.10	20.92
633026	Drill Core	<0.01	0.13	<0.01	2.81	2.59	
633027	Drill Core	<0.01	0.21	<0.01	1.58	2.46	
633028	Drill Core	<0.01	0.56	<0.01	1.24	2.25	
633029	Drill Core	<0.01	0.39	<0.01	1.13	2.35	
633030	Rock Pulp	0.55	0.29	<0.01	2.08	N.A.	



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: December 13, 2010

Page: 3 of 4 Part 1

CERTIFICATE OF ANALYSIS

WHI10000659.1

	Method Analyte Unit MDL	WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD
		Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg	Al
		kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%	%
		0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01	0.01
633031	Drill Core	0.97	0.009	0.005	0.50	1.30	<2	0.015	<0.001	0.01	2.27	<0.02	<0.01	0.003	<0.01	<0.01	2.08	0.05	0.003	0.14	1.77
633032	Drill Core	0.86	0.005	0.019	2.81	18.15	4	0.009	<0.001	0.06	10.27	<0.02	<0.01	0.049	<0.01	<0.01	6.01	0.07	0.001	0.08	0.66
633033	Drill Core	1.77	<0.001	0.002	1.23	1.23	<2	0.003	<0.001	0.05	2.95	<0.02	0.01	0.004	<0.01	<0.01	24.18	0.07	<0.001	0.09	0.22
633034	Drill Core	2.86	<0.001	<0.001	0.05	0.13	<2	<0.001	<0.001	0.06	0.29	<0.02	0.02	<0.001	<0.01	<0.01	33.70	0.03	<0.001	0.11	0.12
633035	Drill Core	1.48	<0.001	<0.001	<0.02	0.04	<2	<0.001	<0.001	0.06	0.27	<0.02	0.02	<0.001	<0.01	<0.01	38.55	0.01	<0.001	0.10	0.01
633036	Drill Core	1.08	<0.001	<0.001	0.17	0.33	<2	0.001	<0.001	0.04	0.44	<0.02	0.02	<0.001	<0.01	<0.01	23.58	0.06	<0.001	0.07	0.25
633037	Drill Core	0.99	<0.001	0.001	0.04	0.23	<2	0.003	<0.001	0.02	0.83	<0.02	<0.01	<0.001	<0.01	<0.01	8.37	0.08	<0.001	0.07	0.41
633038	Drill Core	2.47	<0.001	<0.001	0.07	0.41	<2	0.001	<0.001	0.05	0.95	<0.02	0.01	0.001	<0.01	<0.01	24.90	0.05	<0.001	0.10	0.24
633039	Drill Core	1.35	0.001	0.004	0.96	4.69	<2	0.006	<0.001	0.02	2.34	<0.02	<0.01	0.013	<0.01	<0.01	7.18	0.09	0.001	0.11	0.90
633040	Drill Core	0.44	0.002	0.005	1.37	9.19	<2	0.003	<0.001	0.05	3.38	<0.02	0.01	0.026	<0.01	<0.01	22.99	0.07	0.001	0.08	0.50
633041	Drill Core	0.46	0.002	0.005	1.43	9.15	<2	0.004	<0.001	0.05	3.90	<0.02	0.01	0.026	<0.01	<0.01	21.19	0.08	0.001	0.09	0.54
633042	Drill Core	0.73	0.002	0.003	2.22	7.56	<2	0.006	<0.001	0.02	2.39	<0.02	<0.01	0.026	<0.01	<0.01	5.39	0.08	0.002	0.14	1.05
633043	Drill Core	2.41	<0.001	0.001	0.97	3.24	<2	0.002	<0.001	0.05	1.71	<0.02	0.02	0.010	<0.01	<0.01	30.39	0.04	<0.001	0.08	0.30
633044	Drill Core	2.28	0.002	0.003	1.08	4.62	<2	0.004	<0.001	0.05	3.71	<0.02	0.01	0.012	<0.01	<0.01	23.07	0.06	0.001	0.10	0.50
633045	Drill Core	1.92	0.002	0.003	0.81	3.62	<2	0.007	<0.001	0.02	2.82	<0.02	<0.01	0.009	<0.01	<0.01	5.52	0.08	0.001	0.10	0.84
633046	Drill Core	2.02	0.002	0.003	0.38	2.44	<2	0.006	<0.001	0.02	2.36	<0.02	<0.01	0.006	<0.01	<0.01	2.58	0.05	<0.001	0.09	0.82
633047	Drill Core	0.89	0.001	0.002	2.17	1.82	<2	0.003	<0.001	0.04	1.55	<0.02	0.01	0.005	<0.01	<0.01	19.68	0.03	0.001	0.09	0.44
633048	Drill Core	2.02	0.003	0.005	1.96	5.61	<2	0.007	<0.001	0.03	3.92	<0.02	<0.01	0.015	<0.01	<0.01	7.38	0.05	0.002	0.10	0.88
633049	Drill Core	2.25	0.003	0.006	1.88	8.12	<2	0.008	<0.001	0.02	3.09	<0.02	<0.01	0.025	<0.01	<0.01	5.66	0.09	0.002	0.11	1.03
633050	Rock	0.29	<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	0.02	0.15	<0.02	0.01	<0.001	<0.01	<0.01	22.83	0.04	<0.001	11.04	0.12
633051	Drill Core	1.60	0.002	0.004	2.58	5.65	<2	0.008	<0.001	0.01	1.72	<0.02	<0.01	0.016	<0.01	<0.01	3.65	0.08	0.001	0.14	1.17
633052	Drill Core	0.69	<0.001	0.002	1.77	5.80	<2	0.002	<0.001	0.03	1.18	<0.02	<0.01	0.022	<0.01	<0.01	16.87	0.03	<0.001	0.06	0.23
633053	Drill Core	1.06	0.001	0.006	3.09	12.75	2	0.005	<0.001	0.02	1.71	<0.02	<0.01	0.040	<0.01	<0.01	6.94	0.07	0.002	0.11	0.79
633054	Drill Core	2.16	0.002	0.003	0.50	0.58	<2	0.007	<0.001	0.02	2.34	<0.02	<0.01	0.002	<0.01	<0.01	13.63	0.15	0.002	0.16	1.17
633055	Drill Core	1.61	<0.001	0.001	0.68	0.04	<2	0.002	<0.001	0.04	0.92	<0.02	0.02	<0.001	<0.01	<0.01	28.34	0.04	<0.001	0.11	0.40
633056	Drill Core	0.69	0.001	0.001	0.03	<0.01	<2	0.005	<0.001	0.02	0.61	<0.02	0.01	<0.001	<0.01	<0.01	18.44	0.09	0.001	0.15	0.96
633057	Drill Core	0.61	<0.001	0.002	1.60	2.88	<2	0.004	<0.001	0.03	0.89	<0.02	0.01	0.010	<0.01	<0.01	24.93	0.09	0.001	0.13	0.73
633058	Drill Core	2.36	0.002	0.002	0.17	0.26	<2	0.007	<0.001	0.02	1.28	<0.02	<0.01	<0.001	<0.01	<0.01	17.63	0.06	0.002	0.15	1.17
633059	Drill Core	0.77	0.002	0.003	2.18	3.65	<2	0.008	<0.001	0.01	1.75	<0.02	<0.01	0.013	<0.01	<0.01	2.26	0.08	0.002	0.13	1.11
633060	Rock Pulp	0.06	<0.001	0.470	1.42	4.28	29	0.001	<0.001	0.64	5.31	<0.02	0.01	0.027	<0.01	<0.01	4.10	0.05	0.003	1.45	4.45



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: December 13, 2010

Page: 3 of 4 **Part** 2

CERTIFICATE OF ANALYSIS

WHI10000659.1

	Method Analyte Unit MDL	7TD	7TD	7TD	7TD	G8SG	7TD.1
		Na	K	W	S	SG	Pb
		%	%	%	%		%
		0.01	0.01	0.01	0.05	0	0.02
633031	Drill Core	<0.01	1.10	<0.01	3.13	2.24	
633032	Drill Core	<0.01	0.38	<0.01	20.24	2.86	
633033	Drill Core	<0.01	0.14	<0.01	4.17	2.57	
633034	Drill Core	<0.01	0.09	<0.01	0.36	2.48	
633035	Drill Core	<0.01	0.05	<0.01	0.29	2.47	
633036	Drill Core	<0.01	0.15	<0.01	0.56	2.46	
633037	Drill Core	<0.01	0.22	<0.01	0.82	2.41	
633038	Drill Core	<0.01	0.15	<0.01	1.22	2.49	
633039	Drill Core	<0.01	0.54	<0.01	5.32	2.42	
633040	Drill Core	<0.01	0.26	<0.01	9.43	2.62	
633041	Drill Core	<0.01	0.28	<0.01	10.10	2.61	
633042	Drill Core	<0.01	0.59	<0.01	7.00	2.45	
633043	Drill Core	<0.01	0.15	<0.01	4.18	2.50	
633044	Drill Core	<0.01	0.26	<0.01	7.40	2.52	
633045	Drill Core	<0.01	0.51	<0.01	5.35	2.41	
633046	Drill Core	<0.01	0.51	<0.01	4.16	2.40	
633047	Drill Core	<0.01	0.26	<0.01	3.28	2.51	
633048	Drill Core	<0.01	0.53	<0.01	8.12	2.51	
633049	Drill Core	<0.01	0.62	<0.01	8.24	2.50	
633050	Rock	0.01	0.02	<0.01	0.17	2.60	
633051	Drill Core	<0.01	0.71	<0.01	5.35	2.40	
633052	Drill Core	<0.01	0.12	<0.01	4.90	2.64	
633053	Drill Core	<0.01	0.45	<0.01	8.97	2.59	
633054	Drill Core	<0.01	0.66	<0.01	3.38	2.43	
633055	Drill Core	<0.01	0.21	<0.01	1.40	2.48	
633056	Drill Core	<0.01	0.52	<0.01	0.77	2.36	
633057	Drill Core	<0.01	0.38	<0.01	3.04	2.49	
633058	Drill Core	<0.01	0.68	<0.01	1.77	2.34	
633059	Drill Core	<0.01	0.66	<0.01	4.16	2.41	
633060	Rock Pulp	0.10	3.08	<0.01	5.38	N.A.	



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: December 13, 2010

Page: 4 of 4 Part 1

CERTIFICATE OF ANALYSIS

WHI10000659.1

	Method Analyte Unit MDL	WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD
		Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg	Al
		kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%	%
		0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01	0.01
633061	Drill Core	1.89	0.005	0.005	1.93	5.70	<2	0.013	<0.001	0.01	2.22	<0.02	<0.01	0.016	<0.01	<0.01	2.49	0.14	0.003	0.17	1.62
633062	Drill Core	1.05	0.001	0.009	6.78	23.34	7	0.002	<0.001	0.02	0.74	<0.02	<0.01	0.069	<0.01	<0.01	11.84	0.08	<0.001	0.04	0.23
633063	Drill Core	2.06	0.002	0.007	4.73	14.73	4	0.008	<0.001	0.02	3.46	<0.02	<0.01	0.040	<0.01	<0.01	1.80	0.08	0.002	0.08	0.79
633064	Drill Core	2.50	0.002	0.013	6.73	27.01	6	0.005	<0.001	0.02	2.54	<0.02	<0.01	0.076	<0.01	<0.01	1.48	0.07	<0.001	0.05	0.40
633065	Drill Core	1.04	0.002	0.003	0.59	1.77	<2	0.006	<0.001	0.03	2.21	<0.02	<0.01	0.004	<0.01	<0.01	14.98	0.05	0.001	0.09	0.53
633066	Drill Core	1.07	0.001	0.001	<0.02	0.05	<2	0.004	<0.001	<0.01	0.59	<0.02	<0.01	<0.001	<0.01	<0.01	1.05	0.04	<0.001	0.05	0.43
633067	Drill Core	0.98	<0.001	0.001	<0.02	<0.01	<2	0.001	<0.001	0.01	1.15	<0.02	0.01	<0.001	<0.01	<0.01	11.07	<0.01	<0.001	0.01	0.29
633068	Drill Core	2.13	0.002	0.003	0.18	0.69	<2	0.007	<0.001	0.02	1.32	<0.02	<0.01	0.002	<0.01	<0.01	12.18	0.07	0.002	0.12	0.88
633069	Drill Core	2.42	<0.001	0.003	0.02	<0.01	<2	0.003	<0.001	0.02	2.20	<0.02	<0.01	<0.001	<0.01	<0.01	15.04	0.02	<0.001	0.05	0.24
633070	Drill Core	0.45	0.002	0.005	0.17	0.09	<2	0.007	<0.001	0.06	2.99	<0.02	0.01	<0.001	<0.01	<0.01	22.62	0.15	0.002	0.15	0.47
633071	Drill Core	0.39	0.003	0.006	0.30	0.10	<2	0.009	<0.001	0.03	3.91	<0.02	<0.01	<0.001	<0.01	<0.01	11.63	0.15	0.002	0.12	0.64
633072	Drill Core	0.66	0.002	0.007	4.47	0.72	14	0.007	<0.001	0.05	2.12	<0.02	0.01	0.002	<0.01	<0.01	18.59	0.41	0.002	0.11	0.51
633073	Drill Core	2.62	0.003	0.007	0.04	0.30	<2	0.007	<0.001	0.02	2.05	<0.02	<0.01	0.001	<0.01	<0.01	9.60	0.43	0.002	0.08	0.57
633074	Drill Core	3.19	0.004	0.009	0.15	0.40	<2	0.008	<0.001	0.03	0.88	<0.02	0.01	0.002	<0.01	<0.01	20.69	0.31	0.003	0.11	0.58
633075	Drill Core	2.19	0.004	0.008	0.09	0.49	<2	0.008	<0.001	0.02	0.90	<0.02	0.01	0.002	<0.01	<0.01	16.01	0.37	0.004	0.11	0.69
633076	Drill Core	2.28	0.006	0.013	0.18	1.43	3	0.014	<0.001	0.01	1.78	<0.02	<0.01	0.005	<0.01	<0.01	5.76	0.38	0.005	0.13	1.05
633077	Drill Core	3.25	0.011	0.014	0.09	0.63	2	0.020	<0.001	<0.01	1.09	<0.02	<0.01	0.003	<0.01	<0.01	2.68	0.19	0.007	0.17	1.44
633078	Drill Core	2.56	0.003	0.012	0.25	0.51	3	0.027	<0.001	<0.01	1.96	<0.02	<0.01	0.002	<0.01	<0.01	8.72	2.84	0.017	0.24	2.12
633079	Drill Core	2.31	<0.001	0.002	<0.02	<0.01	<2	0.002	<0.001	0.03	2.16	<0.02	0.02	<0.001	<0.01	<0.01	23.28	0.06	0.003	0.35	2.45
633080	Rock	0.40	<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	0.02	0.22	<0.02	0.01	<0.001	<0.01	<0.01	21.29	0.03	<0.001	11.24	0.18
633081	Drill Core	1.67	<0.001	<0.001	<0.02	<0.01	<2	0.001	<0.001	0.04	1.06	<0.02	0.02	<0.001	<0.01	<0.01	30.74	0.02	0.002	0.30	1.81



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: December 13, 2010

Page: 4 of 4 **Part** 2

CERTIFICATE OF ANALYSIS

WHI10000659.1

	Method Analyte Unit MDL	7TD	7TD	7TD	7TD	G8SG	7TD.1
		Na	K	W	S	SG	Pb
		%	%	%	%		%
		0.01	0.01	0.01	0.05	0	0.02
633061	Drill Core	<0.01	1.05	<0.01	5.82	2.36	
633062	Drill Core	<0.01	0.13	<0.01	13.92	2.89	
633063	Drill Core	<0.01	0.48	<0.01	12.16	2.65	
633064	Drill Core	<0.01	0.24	<0.01	17.49	2.93	
633065	Drill Core	<0.01	0.35	<0.01	3.72	2.46	
633066	Drill Core	<0.01	0.24	<0.01	0.36	2.42	
633067	Drill Core	<0.01	0.30	<0.01	1.35	2.52	
633068	Drill Core	<0.01	0.52	<0.01	1.94	2.35	
633069	Drill Core	<0.01	0.13	<0.01	2.76	2.48	
633070	Drill Core	<0.01	0.27	<0.01	4.01	2.47	
633071	Drill Core	<0.01	0.37	<0.01	5.09	2.41	
633072	Drill Core	<0.01	0.30	<0.01	3.97	2.50	
633073	Drill Core	<0.01	0.34	<0.01	2.46	2.35	
633074	Drill Core	<0.01	0.33	<0.01	1.37	2.37	
633075	Drill Core	<0.01	0.39	<0.01	1.35	2.31	
633076	Drill Core	<0.01	0.63	<0.01	2.72	2.27	
633077	Drill Core	<0.01	0.87	<0.01	1.54	2.22	
633078	Drill Core	<0.01	1.39	<0.01	2.59	1.98	
633079	Drill Core	<0.01	1.55	<0.01	2.77	2.51	
633080	Rock	0.01	0.03	<0.01	0.21	2.57	
633081	Drill Core	<0.01	1.10	<0.01	1.44	2.52	



Acme Analytical Laboratories (Vancouver) Ltd.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: Selwyn Resources Ltd.

Suite 700 - 509 Richards Street

Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: December 13, 2010

Page: 1 of 2 Part 1

QUALITY CONTROL REPORT

WHI10000659.1

	Method Analyte Unit MDL	WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD
		Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg	Al
		kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%	%
		0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01	0.01
Pulp Duplicates																					
633032	Drill Core	0.86	0.005	0.019	2.81	18.15	4	0.009	<0.001	0.06	10.27	<0.02	<0.01	0.049	<0.01	<0.01	6.01	0.07	0.001	0.08	0.66
REP 633032	QC		0.004	0.019	2.77	17.91	4	0.009	<0.001	0.06	10.28	<0.02	<0.01	0.049	<0.01	<0.01	5.99	0.07	0.002	0.08	0.68
633069	Drill Core	2.42	<0.001	0.003	0.02	<0.01	<2	0.003	<0.001	0.02	2.20	<0.02	<0.01	<0.001	<0.01	<0.01	15.04	0.02	<0.001	0.05	0.24
REP 633069	QC		<0.001	0.003	0.02	<0.01	<2	0.003	<0.001	0.03	2.29	<0.02	<0.01	<0.001	<0.01	<0.01	15.92	0.03	<0.001	0.05	0.25
Core Reject Duplicates																					
633003	Drill Core	1.04	<0.001	0.007	0.17	1.67	3	0.012	<0.001	0.01	1.82	<0.02	0.01	0.005	<0.01	<0.01	8.52	1.65	0.009	0.53	3.14
DUP 633003	QC		<0.001	0.008	0.18	1.82	3	0.014	<0.001	0.01	1.83	<0.02	0.01	0.005	<0.01	<0.01	8.36	1.59	0.010	0.53	3.09
633038	Drill Core	2.47	<0.001	<0.001	0.07	0.41	<2	0.001	<0.001	0.05	0.95	<0.02	0.01	0.001	<0.01	<0.01	24.90	0.05	<0.001	0.10	0.24
DUP 633038	QC		<0.001	<0.001	0.08	0.43	<2	0.002	<0.001	0.05	0.96	<0.02	0.01	0.001	<0.01	<0.01	24.94	0.06	<0.001	0.10	0.28
633073	Drill Core	2.62	0.003	0.007	0.04	0.30	<2	0.007	<0.001	0.02	2.05	<0.02	<0.01	0.001	<0.01	<0.01	9.60	0.43	0.002	0.08	0.57
DUP 633073	QC		0.003	0.007	0.05	0.31	<2	0.007	<0.001	0.02	2.07	<0.02	<0.01	0.001	<0.01	<0.01	9.64	0.43	0.002	0.08	0.57
Reference Materials																					
STD CCU-1C	Standard																				
STD CZN-3	Standard																				
STD OREAS131A	Standard		<0.001	0.033	1.76	2.94	32	0.002	0.002	0.18	5.91	<0.02	<0.01	0.008	<0.01	<0.01	5.46	0.06	0.003	3.20	4.72
STD OREAS131A	Standard		<0.001	0.033	1.70	2.93	31	0.003	0.002	0.18	5.98	<0.02	<0.01	0.009	<0.01	<0.01	5.57	0.06	0.003	3.24	4.62
STD OREAS131A	Standard		<0.001	0.032	1.72	2.87	31	0.003	0.002	0.18	5.94	<0.02	<0.01	0.008	<0.01	<0.01	5.46	0.06	0.002	3.19	4.54
STD OREAS131A	Standard		<0.001	0.032	1.65	2.81	31	0.003	0.002	0.17	5.82	<0.02	<0.01	0.008	<0.01	<0.01	5.35	0.06	0.002	3.05	4.47
STD PTC-1A	Standard																				
STD R4T	Standard		0.069	0.523	1.62	3.54	90	0.362	0.044	0.09	24.75	<0.02	0.02	0.019	0.02	<0.01	2.28	0.05	0.019	1.46	4.03
STD R4T	Standard		0.066	0.527	1.60	3.57	90	0.361	0.044	0.10	25.21	<0.02	0.02	0.021	0.02	<0.01	2.31	0.05	0.017	1.51	4.06
STD R4T	Standard		0.064	0.521	1.62	3.51	88	0.358	0.041	0.10	24.87	<0.02	0.02	0.019	0.02	<0.01	2.27	0.05	0.017	1.50	4.03
STD R4T	Standard		0.065	0.518	1.58	3.51	89	0.358	0.044	0.09	24.80	<0.02	0.02	0.020	0.02	<0.01	2.22	0.05	0.020	1.43	3.99
STD SARM 71	Standard																				
STD SU-1B	Standard		<0.001	1.161	<0.02	0.03	6	1.997	0.067	0.07	25.84	<0.02	0.03	<0.001	<0.01	<0.01	2.27	0.06	0.031	1.85	4.51
STD SU-1B	Standard		<0.001	1.204	<0.02	0.03	7	1.961	0.068	0.07	25.67	<0.02	0.03	<0.001	<0.01	<0.01	2.27	0.07	0.027	1.83	4.37
STD SU-1B	Standard		<0.001	1.161	<0.02	0.03	7	1.929	0.066	0.07	25.35	<0.02	0.03	<0.001	<0.01	<0.01	2.23	0.06	0.028	1.80	4.31
STD SU-1B	Standard		<0.001	1.172	<0.02	0.03	7	1.944	0.067	0.07	25.74	<0.02	0.03	<0.001	<0.01	<0.01	2.22	0.08	0.032	1.78	4.37



Acme Analytical Laboratories (Vancouver) Ltd.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: **Selwyn Resources Ltd.**

Suite 700 - 509 Richards Street

Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: December 13, 2010

Page: 1 of 2 **Part** 2

QUALITY CONTROL REPORT

WHI10000659.1

Method		7TD	7TD	7TD	7TD	G8SG	7TD.1
Analyte		Na	K	W	S	SG	Pb
Unit		%	%	%	%		%
MDL		0.01	0.01	0.01	0.05	0	0.02
Pulp Duplicates							
633032	Drill Core	<0.01	0.38	<0.01	20.24	2.86	
REP 633032	QC	<0.01	0.38	<0.01	20.01		
633069	Drill Core	<0.01	0.13	<0.01	2.76	2.48	
REP 633069	QC	<0.01	0.13	<0.01	2.88		
Core Reject Duplicates							
633003	Drill Core	0.01	2.07	<0.01	2.69	2.24	
DUP 633003	QC	0.01	2.04	<0.01	2.79	2.27	
633038	Drill Core	<0.01	0.15	<0.01	1.22	2.49	
DUP 633038	QC	<0.01	0.15	<0.01	1.51	2.49	
633073	Drill Core	<0.01	0.34	<0.01	2.46	2.35	
DUP 633073	QC	<0.01	0.34	<0.01	2.55	2.34	
Reference Materials							
STD CCU-1C	Standard						0.41
STD CZN-3	Standard						0.13
STD OREAS131A	Standard	0.16	3.44	<0.01	4.77		
STD OREAS131A	Standard	0.16	3.51	<0.01	5.10		
STD OREAS131A	Standard	0.16	3.49	<0.01	4.86		
STD OREAS131A	Standard	0.15	3.36	<0.01	5.16		
STD PTC-1A	Standard						0.05
STD R4T	Standard	0.94	1.21	<0.01	12.10		
STD R4T	Standard	0.98	1.24	<0.01	14.04		
STD R4T	Standard	0.97	1.22	<0.01	13.21		
STD R4T	Standard	0.96	1.23	<0.01	13.07		
STD SARM 71	Standard						<0.02
STD SU-1B	Standard	1.72	0.63	<0.01	8.36		
STD SU-1B	Standard	1.73	0.64	<0.01	10.60		
STD SU-1B	Standard	1.70	0.62	<0.01	8.49		
STD SU-1B	Standard	1.81	0.64	<0.01	9.19		



Acme Analytical Laboratories (Vancouver) Ltd.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: **Selwyn Resources Ltd.**

Suite 700 - 509 Richards Street

Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: December 13, 2010

Page: 2 of 2 Part 1

QUALITY CONTROL REPORT

WHI10000659.1

		WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD
		Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg	Al
		kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%	%
		0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01	0.01
STD R4T Expected			0.062	0.502	1.518	3.376	86	0.339	0.039	0.086	24.07	0.0087	0.0185	0.018	0.0138	0.0018	2.166	0.045	0.018	1.384	3.897
STD OREAS131A Expected			0.001	0.0322	1.72	2.83	30.9	0.0027	0.0023	0.1722	5.8166	0.0082	0.0028	0.0081	0.0047	0.001	5.286	0.0536	0.0025	3.1182	4.6057
STD SU-1B Expected			0.0004	1.185	0.0058	0.0235	6.4	1.97	0.0672	0.0703	25.54	0.00025	0.03	0.0003	0.00002	0.0003	2.21	0.06	0.032	1.79	4.39
STD CZN-3 Expected																					
STD CCU-1C Expected																					
STD PTC-1A Expected																					
BLK	Blank		<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	<0.01	<0.01	<0.02	<0.01	<0.001	<0.01	<0.01	<0.01	<0.01	<0.001	<0.01	<0.01
BLK	Blank		<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	<0.01	<0.01	<0.02	<0.01	<0.001	<0.01	<0.01	<0.01	<0.01	<0.001	<0.01	<0.01
BLK	Blank		<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	<0.01	<0.01	<0.02	<0.01	<0.001	<0.01	<0.01	<0.01	<0.01	<0.001	<0.01	<0.01
BLK	Blank		<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	<0.01	<0.01	<0.02	<0.01	<0.001	<0.01	<0.01	<0.01	<0.01	<0.001	<0.01	<0.01
BLK	Blank																				
Prep Wash																					
G1	Prep Blank		<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	0.08	2.44	<0.02	0.08	<0.001	<0.01	<0.01	2.50	0.08	<0.001	0.61	7.66
G1	Prep Blank		<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	0.08	2.45	<0.02	0.08	<0.001	<0.01	<0.01	2.47	0.08	<0.001	0.59	7.58



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**

Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: December 13, 2010

Page: 2 of 2 **Part** 2

QUALITY CONTROL REPORT

WHI10000659.1

		7TD Na %	7TD K %	7TD W %	7TD S %	G8SG SG %	7TD.1 Pb %
		0.01	0.01	0.01	0.05	0	0.02
STD R4T Expected		0.9	1.153	0.00016	12.9903		
STD OREAS131A Expected		0.1501	3.1584	0.0005	4.8		
STD SU-1B Expected		1.662	0.6	0.0007	8.76		
STD CZN-3 Expected							0.113
STD CCU-1C Expected							0.34
STD PTC-1A Expected							0.05
BLK	Blank	<0.01	<0.01	<0.01	<0.05		
BLK	Blank	<0.01	<0.01	<0.01	<0.05		
BLK	Blank	<0.01	<0.01	<0.01	<0.05		
BLK	Blank	<0.01	<0.01	<0.01	<0.05		
BLK	Blank						<0.02
Prep Wash							
G1	Prep Blank	2.88	3.05	<0.01	<0.05	2.70	
G1	Prep Blank	2.85	3.07	<0.01	<0.05	2.68	



1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**

Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Submitted By: Jason K. Dunning

Receiving Lab: Canada-Whitehorse

Received: November 22, 2010

Report Date: December 05, 2010

Page: 1 of 3

CERTIFICATE OF ANALYSIS

WHI10000658.1

CLIENT JOB INFORMATION

Project: Selwyn Project
Shipment ID:
P.O. Number 1062
Number of Samples: 33

SAMPLE DISPOSAL

STOR-PLP Store After 90 days Invoice for Storage
STOR-RJT Store After 90 days Invoice for Storage

Acme does not accept responsibility for samples left at the laboratory after 90 days without prior written instructions for sample storage or return.

Invoice To: Selwyn Resources Ltd.
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6
Canada

CC:

SAMPLE PREPARATION AND ANALYTICAL PROCEDURES

Method Code	Number of Samples	Code Description	Test Wgt (g)	Report Status	Lab
R200-250	32	Crush split and pulverize 250g drill core to 200 mesh			WHI
7TD2	33	4 Acid digestion ICP-ES analysis.	0.5	Completed	VAN
G812	33	Specific Gravity on Pulp		Completed	VAN

ADDITIONAL COMMENTS



This report supersedes all previous preliminary and final reports with this file number dated prior to the date on this certificate. Signature indicates final approval; preliminary reports are unsigned and should be used for reference only.
All results are considered the confidential property of the client. Acme assumes the liabilities for actual cost of analysis only.
** asterisk indicates that an analytical result could not be provided due to unusually high levels of interference from other elements.



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: December 05, 2010

Page: 2 of 3 Part 1

CERTIFICATE OF ANALYSIS

WHI10000658.1

	Method Analyte Unit MDL	WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD
		Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg	Al
		kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%	%
		0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01	0.01
631801	Drill Core	1.29	<0.001	0.001	0.04	0.06	<2	0.002	<0.001	0.03	0.51	<0.02	0.01	<0.001	<0.01	<0.01	18.92	0.23	<0.001	0.15	0.42
631802	Drill Core	0.81	0.001	0.004	0.05	1.29	<2	0.006	<0.001	<0.01	0.79	<0.02	<0.01	0.005	<0.01	<0.01	2.22	0.28	0.002	0.13	1.10
631803	Drill Core	0.84	0.003	0.005	0.08	0.18	4	0.010	<0.001	<0.01	2.49	<0.02	<0.01	<0.001	<0.01	<0.01	0.56	0.09	0.002	0.13	1.47
631804	Drill Core	1.63	0.002	0.009	3.53	9.05	4	0.005	<0.001	0.01	3.54	<0.02	<0.01	0.044	<0.01	<0.01	0.30	0.02	<0.001	0.06	0.66
631805	Drill Core	1.00	0.006	0.010	1.13	6.48	5	0.013	<0.001	0.01	5.63	<0.02	<0.01	0.018	<0.01	<0.01	0.24	0.06	0.003	0.14	1.98
631806	Drill Core	1.11	0.002	0.004	2.18	6.32	<2	0.005	<0.001	0.03	2.24	<0.02	<0.01	0.015	<0.01	<0.01	4.30	0.03	0.001	0.08	0.59
631807	Drill Core	1.49	0.004	0.006	1.43	5.24	<2	0.007	<0.001	0.04	3.90	<0.02	<0.01	0.013	<0.01	<0.01	16.81	0.07	0.002	0.10	0.93
631808	Drill Core	1.58	0.001	0.003	0.93	3.05	<2	0.004	<0.001	0.04	2.34	<0.02	<0.01	0.008	<0.01	<0.01	14.66	0.04	0.001	0.08	0.37
631809	Drill Core	0.65	<0.001	0.001	0.05	0.45	<2	0.002	<0.001	0.02	0.47	<0.02	<0.01	0.001	<0.01	<0.01	17.01	0.03	<0.001	0.04	0.22
631810	Drill Core	1.05	<0.001	0.001	0.09	0.42	<2	0.002	<0.001	0.01	0.51	<0.02	0.01	0.001	<0.01	<0.01	11.82	0.02	<0.001	0.02	0.24
631811	Drill Core	0.87	<0.001	0.001	0.27	0.65	<2	0.002	<0.001	0.01	0.57	<0.02	0.01	0.002	<0.01	<0.01	13.42	0.02	<0.001	0.03	0.26
631812	Drill Core	1.30	0.006	0.003	0.16	1.01	<2	0.012	<0.001	0.02	2.03	<0.02	<0.01	0.003	<0.01	<0.01	9.07	0.05	0.002	0.12	1.38
631813	Drill Core	0.80	0.004	0.014	2.57	15.46	3	0.008	<0.001	0.03	8.21	<0.02	<0.01	0.039	<0.01	<0.01	2.12	0.07	0.002	0.06	0.65
631814	Drill Core	2.55	<0.001	0.002	1.85	1.60	<2	0.002	<0.001	0.05	2.78	<0.02	0.01	0.005	<0.01	<0.01	20.88	0.05	0.001	0.09	0.31
631815	Drill Core	1.76	0.001	0.004	2.01	7.87	<2	0.007	<0.001	0.02	2.66	<0.02	<0.01	0.022	<0.01	<0.01	1.69	0.08	0.002	0.11	0.98
631816	Drill Core	0.76	<0.001	0.002	1.40	2.94	<2	0.004	<0.001	0.02	2.52	<0.02	<0.01	0.009	<0.01	<0.01	7.77	0.04	0.002	0.07	0.64
631817	Drill Core	1.91	<0.001	0.001	0.29	1.19	<2	0.002	<0.001	0.04	0.83	<0.02	0.02	0.003	<0.01	<0.01	32.58	0.03	<0.001	0.09	0.27
631818	Drill Core	0.49	0.001	0.002	0.83	3.73	<2	0.005	<0.001	0.03	3.78	<0.02	<0.01	0.010	<0.01	<0.01	6.90	0.05	0.001	0.12	0.64
631819	Drill Core	0.47	0.002	0.002	2.35	4.50	<2	0.004	<0.001	0.04	1.28	<0.02	0.01	0.011	<0.01	<0.01	26.05	0.05	0.002	0.15	0.58
631820	Rock	0.37	<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	0.01	0.14	<0.02	0.01	<0.001	<0.01	<0.01	21.82	0.03	<0.001	10.85	0.14
631821	Drill Core	0.72	<0.001	0.002	4.51	14.38	2	0.002	<0.001	0.02	0.83	<0.02	<0.01	0.052	<0.01	<0.01	6.91	0.03	0.002	0.08	0.31
631822	Drill Core	3.04	0.003	0.005	3.08	11.55	3	0.007	<0.001	0.02	2.98	<0.02	<0.01	0.033	<0.01	<0.01	3.30	0.07	0.002	0.10	0.78
631823	Drill Core	1.40	0.002	0.005	2.97	9.29	3	0.006	<0.001	0.03	2.04	<0.02	<0.01	0.027	<0.01	<0.01	7.05	0.05	0.002	0.09	0.76
631824	Drill Core	0.89	<0.001	<0.001	0.68	0.11	<2	0.002	<0.001	0.07	0.48	<0.02	0.02	<0.001	<0.01	<0.01	29.53	0.03	<0.001	0.11	0.35
631825	Drill Core	2.71	<0.001	0.002	0.05	0.07	<2	0.004	<0.001	0.03	1.26	<0.02	0.01	<0.001	<0.01	<0.01	22.96	0.04	0.001	0.11	0.54
631826	Drill Core	2.11	0.003	0.004	1.19	0.89	<2	0.007	<0.001	0.02	0.83	<0.02	<0.01	0.003	<0.01	<0.01	9.20	0.06	0.003	0.13	1.01
631827	Drill Core	1.15	0.001	0.003	<0.02	0.09	<2	0.005	<0.001	<0.01	0.67	<0.02	<0.01	<0.001	<0.01	<0.01	2.62	0.05	<0.001	0.07	0.54
631828	Drill Core	3.54	<0.001	0.003	<0.02	0.05	<2	0.003	<0.001	0.05	0.66	<0.02	0.02	<0.001	<0.01	<0.01	26.46	0.03	<0.001	0.08	0.37
631829	Drill Core	1.33	0.002	0.006	0.24	1.50	<2	0.009	<0.001	0.02	1.33	<0.02	<0.01	0.003	<0.01	<0.01	5.74	0.06	0.002	0.11	0.79
631830	Rock Pulp	0.06	<0.001	0.668	6.11	7.07	70	<0.001	0.001	0.10	5.03	<0.02	0.02	0.019	0.03	<0.01	1.38	0.02	0.002	0.25	4.90



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: December 05, 2010

Page: 2 of 3 **Part** 2

CERTIFICATE OF ANALYSIS

WHI10000658.1

	Method	7TD	7TD	7TD	7TD	G8SG
	Analyte	Na	K	W	S	SG
	Unit	%	%	%	%	
	MDL	0.01	0.01	0.01	0.05	0
631801	Drill Core	<0.01	0.22	<0.01	0.51	2.51
631802	Drill Core	<0.01	0.61	<0.01	1.19	2.45
631803	Drill Core	<0.01	0.93	<0.01	2.66	2.39
631804	Drill Core	<0.01	0.40	<0.01	8.87	2.79
631805	Drill Core	<0.01	1.32	<0.01	9.76	2.47
631806	Drill Core	<0.01	0.33	<0.01	5.82	2.59
631807	Drill Core	<0.01	0.62	<0.01	7.61	2.60
631808	Drill Core	<0.01	0.20	<0.01	4.43	2.54
631809	Drill Core	<0.01	0.11	<0.01	0.78	2.50
631810	Drill Core	<0.01	0.16	<0.01	0.67	2.54
631811	Drill Core	<0.01	0.16	<0.01	0.97	2.59
631812	Drill Core	<0.01	0.91	<0.01	2.87	2.23
631813	Drill Core	<0.01	0.37	<0.01	16.61	2.73
631814	Drill Core	<0.01	0.16	<0.01	4.48	2.68
631815	Drill Core	<0.01	0.60	<0.01	6.85	2.53
631816	Drill Core	<0.01	0.38	<0.01	4.33	2.56
631817	Drill Core	<0.01	0.13	<0.01	1.86	2.54
631818	Drill Core	<0.01	0.30	<0.01	6.08	2.50
631819	Drill Core	<0.01	0.28	<0.01	4.23	2.56
631820	Rock	0.01	0.03	<0.01	0.20	2.64
631821	Drill Core	<0.01	0.16	<0.01	8.37	2.76
631822	Drill Core	<0.01	0.46	<0.01	9.11	2.58
631823	Drill Core	<0.01	0.44	<0.01	7.17	2.54
631824	Drill Core	<0.01	0.18	<0.01	0.87	2.46
631825	Drill Core	<0.01	0.27	<0.01	1.58	2.45
631826	Drill Core	<0.01	0.60	<0.01	1.33	2.33
631827	Drill Core	<0.01	0.34	<0.01	0.44	2.33
631828	Drill Core	<0.01	0.19	<0.01	0.87	2.37
631829	Drill Core	<0.01	0.41	<0.01	1.98	2.34
631830	Rock Pulp	2.37	1.38	<0.01	5.78	N.A.



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: December 05, 2010

Page: 3 of 3 **Part** 1

CERTIFICATE OF ANALYSIS

WHI10000658.1

	Method Analyte Unit MDL	WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD
		Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg
		kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%
		0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01
631831	Drill Core	2.81	0.003	0.011	0.25	0.62	<2	0.007	<0.001	0.04	3.27	<0.02	0.02	0.002	<0.01	<0.01	24.31	1.16	0.003	0.13
631832	Drill Core	1.80	0.003	0.007	0.03	0.07	<2	0.005	<0.001	0.04	0.87	<0.02	0.01	<0.001	<0.01	<0.01	24.06	0.45	0.002	0.09
631833	Drill Core	0.74	0.008	0.009	0.28	1.07	3	0.013	<0.001	0.02	0.76	<0.02	<0.01	0.004	<0.01	<0.01	10.67	0.23	0.006	0.16



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: December 05, 2010

Page: 3 of 3 **Part** 2

CERTIFICATE OF ANALYSIS

WHI10000658.1

		Method	7TD	7TD	7TD	7TD	G8SG
		Analyte	Na	K	W	S	SG
		Unit	%	%	%	%	
		MDL	0.01	0.01	0.01	0.05	0
631831	Drill Core		<0.01	0.24	<0.01	4.23	2.40
631832	Drill Core		<0.01	0.15	<0.01	1.16	2.37
631833	Drill Core		<0.01	0.70	<0.01	1.29	2.23



Acme Analytical Laboratories (Vancouver) Ltd.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: Selwyn Resources Ltd.

Suite 700 - 509 Richards Street

Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: December 05, 2010

Page: 1 of 1 Part 1

QUALITY CONTROL REPORT

WHI10000658.1

	Method Analyte Unit MDL	WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD
		Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg	Al
		kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%	%
		0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01	0.01
Pulp Duplicates																					
631811	Drill Core	0.87	<0.001	0.001	0.27	0.65	<2	0.002	<0.001	0.01	0.57	<0.02	0.01	0.002	<0.01	<0.01	13.42	0.02	<0.001	0.03	0.26
REP 631811	QC		<0.001	0.001	0.27	0.65	<2	0.002	<0.001	0.01	0.58	<0.02	0.01	0.002	<0.01	<0.01	13.67	0.02	<0.001	0.03	0.26
Core Reject Duplicates																					
631815	Drill Core	1.76	0.001	0.004	2.01	7.87	<2	0.007	<0.001	0.02	2.66	<0.02	<0.01	0.022	<0.01	<0.01	1.69	0.08	0.002	0.11	0.98
DUP 631815	QC		0.001	0.004	1.88	7.99	<2	0.006	<0.001	0.02	2.57	<0.02	<0.01	0.023	<0.01	<0.01	1.79	0.08	0.002	0.11	0.97
Reference Materials																					
STD OREAS131A	Standard		<0.001	0.033	1.78	2.93	31	0.003	0.002	0.18	5.86	<0.02	<0.01	0.008	<0.01	<0.01	5.40	0.05	0.002	3.20	4.75
STD OREAS131A	Standard		<0.001	0.032	1.72	2.87	31	0.003	0.002	0.18	5.94	<0.02	<0.01	0.008	<0.01	<0.01	5.46	0.06	0.002	3.19	4.54
STD R4T	Standard		0.065	0.516	1.62	3.47	88	0.359	0.041	0.09	24.29	<0.02	0.02	0.019	0.02	<0.01	2.23	0.04	0.018	1.45	4.06
STD R4T	Standard		0.064	0.521	1.62	3.51	88	0.358	0.041	0.10	24.87	<0.02	0.02	0.019	0.02	<0.01	2.27	0.05	0.017	1.50	4.03
STD SU-1B	Standard		<0.001	1.191	0.03	0.03	7	1.973	0.067	0.07	25.51	<0.02	0.03	<0.001	<0.01	<0.01	2.28	0.06	0.031	1.82	4.49
STD SU-1B	Standard		<0.001	1.161	<0.02	0.03	7	1.929	0.066	0.07	25.35	<0.02	0.03	<0.001	<0.01	<0.01	2.23	0.06	0.028	1.80	4.31
STD R4T Expected			0.062	0.502	1.518	3.376	86	0.339	0.039	0.086	24.07	0.0087	0.0185	0.018	0.0138	0.0018	2.166	0.045	0.018	1.384	3.897
STD OREAS131A Expected			0.001	0.0322	1.72	2.83	30.9	0.0027	0.0023	0.1722	5.8166	0.0082	0.0028	0.0081	0.0047	0.001	5.286	0.0536	0.0025	3.1182	4.6057
STD SU-1B Expected			0.0004	1.185	0.0058	0.0235	6.4	1.97	0.0672	0.0703	25.54	0.00025	0.03	0.0003	0.00002	0.0003	2.21	0.06	0.032	1.79	4.39
BLK	Blank		<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	<0.01	<0.01	<0.02	<0.01	<0.001	<0.01	<0.01	<0.01	<0.01	<0.001	<0.01	<0.01
BLK	Blank		<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	<0.01	<0.01	<0.02	<0.01	<0.001	<0.01	<0.01	<0.01	<0.01	<0.001	<0.01	<0.01
Prep Wash																					
G1	Prep Blank		<0.001	<0.001	0.03	<0.01	<2	<0.001	<0.001	0.07	2.30	<0.02	0.07	<0.001	<0.01	<0.01	2.22	0.08	<0.001	0.59	6.27
G1	Prep Blank		<0.001	<0.001	0.03	<0.01	<2	<0.001	<0.001	0.08	2.42	<0.02	0.07	<0.001	<0.01	<0.01	2.31	0.07	<0.001	0.61	6.91



Acme Analytical Laboratories (Vancouver) Ltd.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: **Selwyn Resources Ltd.**

Suite 700 - 509 Richards Street

Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: December 05, 2010

Page: 1 of 1 Part 2

QUALITY CONTROL REPORT

WHI10000658.1

		Method	7TD	7TD	7TD	7TD	G8SG
		Analyte	Na	K	W	S	SG
		Unit	%	%	%	%	
		MDL	0.01	0.01	0.01	0.05	0
Pulp Duplicates							
631811	Drill Core		<0.01	0.16	<0.01	0.97	2.59
REP 631811	QC		<0.01	0.16	<0.01	0.98	
Core Reject Duplicates							
631815	Drill Core		<0.01	0.60	<0.01	6.85	2.53
DUP 631815	QC		<0.01	0.59	<0.01	6.74	2.53
Reference Materials							
STD OREAS131A	Standard		0.16	3.45	<0.01	4.77	
STD OREAS131A	Standard		0.16	3.49	<0.01	4.86	
STD R4T	Standard		0.92	1.19	<0.01	12.71	
STD R4T	Standard		0.97	1.22	<0.01	13.21	
STD SU-1B	Standard		1.73	0.62	<0.01	8.25	
STD SU-1B	Standard		1.70	0.62	<0.01	8.49	
STD R4T Expected			0.9	1.153	0.00016	12.9903	
STD OREAS131A Expected			0.1501	3.1584	0.0005	4.8	
STD SU-1B Expected			1.662	0.6	0.0007	8.76	
BLK	Blank		<0.01	<0.01	<0.01	<0.05	
BLK	Blank		<0.01	<0.01	<0.01	<0.05	
Prep Wash							
G1	Prep Blank		2.64	2.94	<0.01	<0.05	2.70
G1	Prep Blank		2.66	2.98	<0.01	<0.05	2.70



1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: Selwyn Resources Ltd.

Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Submitted By: Jason K. Dunning

Receiving Lab: Canada-Whitehorse

Received: November 22, 2010

Report Date: December 13, 2010

Page: 1 of 2

CERTIFICATE OF ANALYSIS

WHI10000657.1

CLIENT JOB INFORMATION

Project: Selwyn Project
Shipment ID:
P.O. Number 1063
Number of Samples: 26

SAMPLE DISPOSAL

STOR-PLP Store After 90 days Invoice for Storage
STOR-RJT Store After 90 days Invoice for Storage

Acme does not accept responsibility for samples left at the laboratory after 90 days without prior written instructions for sample storage or return.

Invoice To: Selwyn Resources Ltd.
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6
Canada

CC:

SAMPLE PREPARATION AND ANALYTICAL PROCEDURES

Method Code	Number of Samples	Code Description	Test Wgt (g)	Report Status	Lab
R200-250	26	Crush split and pulverize 250g drill core to 200 mesh			WHI
7TD2	26	4 Acid digestion ICP-ES analysis.	0.5	Completed	VAN
G812	26	Specific Gravity on Pulp		Completed	VAN
7TD.1	1	4 Acid digestion ICP-ES analysis	0.1	Completed	VAN

ADDITIONAL COMMENTS



This report supersedes all previous preliminary and final reports with this file number dated prior to the date on this certificate. Signature indicates final approval; preliminary reports are unsigned and should be used for reference only.
All results are considered the confidential property of the client. Acme assumes the liabilities for actual cost of analysis only.
** asterisk indicates that an analytical result could not be provided due to unusually high levels of interference from other elements.



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: December 13, 2010

Page: 2 of 2 Part 1

CERTIFICATE OF ANALYSIS

WHI10000657.1

	Method Analyte Unit MDL	WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD
		Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg
		kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%
		0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01
631151	Drill Core	1.77	<0.001	0.005	0.11	0.11	<2	0.011	<0.001	0.02	1.43	<0.02	0.02	<0.001	<0.01	<0.01	13.92	2.10	0.008	0.61
631152	Drill Core	0.66	<0.001	0.015	1.54	10.80	14	0.007	<0.001	0.01	6.36	<0.02	<0.01	0.029	<0.01	<0.01	3.50	0.02	0.002	0.16
631153	Drill Core	0.38	<0.001	0.010	0.35	4.58	5	0.009	<0.001	<0.01	4.78	<0.02	<0.01	0.011	<0.01	<0.01	3.24	1.21	0.006	0.34
631154	Drill Core	0.66	<0.001	0.008	0.05	0.15	<2	0.010	<0.001	0.01	1.58	<0.02	<0.01	<0.001	<0.01	<0.01	5.61	1.26	0.007	0.69
631155	Drill Core	1.85	0.001	0.004	0.05	0.18	<2	0.008	<0.001	<0.01	0.97	<0.02	<0.01	<0.001	<0.01	<0.01	2.14	0.47	0.004	0.19
631156	Drill Core	0.94	<0.001	0.002	0.04	0.12	<2	0.004	<0.001	<0.01	0.70	<0.02	<0.01	<0.001	<0.01	<0.01	1.99	0.76	0.002	0.12
631157	Drill Core	0.91	0.002	0.005	0.39	0.30	<2	0.008	<0.001	0.01	1.28	<0.02	<0.01	0.001	<0.01	<0.01	4.59	0.18	0.003	0.15
631158	Drill Core	0.66	<0.001	0.002	0.04	0.02	<2	0.003	<0.001	0.04	0.32	<0.02	0.02	<0.001	<0.01	<0.01	29.48	0.04	<0.001	0.08
631159	Drill Core	1.06	0.001	0.010	1.09	0.93	2	0.007	<0.001	0.04	5.14	<0.02	0.01	0.002	<0.01	<0.01	17.45	0.55	<0.001	0.08
631160	Drill Core	1.05	0.002	0.007	0.09	0.21	<2	0.005	<0.001	0.03	1.99	<0.02	0.02	<0.001	<0.01	<0.01	21.30	0.65	0.002	0.08
631161	Drill Core	0.90	0.003	0.011	0.26	0.39	<2	0.007	<0.001	0.03	2.10	<0.02	0.02	0.001	<0.01	<0.01	19.69	1.32	0.002	0.08
631162	Drill Core	1.06	0.003	0.010	1.02	3.22	3	0.008	<0.001	0.03	6.07	<0.02	<0.01	0.010	<0.01	<0.01	11.47	0.11	0.002	0.10
631163	Drill Core	0.45	0.002	0.003	3.62	7.55	3	0.005	<0.001	0.03	2.32	<0.02	<0.01	0.026	<0.01	<0.01	10.52	0.05	<0.001	0.09
631164	Drill Core	0.81	<0.001	0.003	>10	21.44	6	0.002	<0.001	0.01	0.52	<0.02	<0.01	0.096	<0.01	<0.01	8.65	0.03	<0.001	0.05
631165	Drill Core	0.78	<0.001	0.004	9.32	24.24	6	<0.001	<0.001	0.02	0.72	<0.02	<0.01	0.101	<0.01	<0.01	14.51	0.01	<0.001	0.03
631166	Drill Core	0.64	<0.001	0.004	6.74	21.66	4	0.003	<0.001	0.02	2.02	<0.02	<0.01	0.082	<0.01	<0.01	8.74	0.04	<0.001	0.05
631167	Drill Core	0.62	0.002	0.003	0.64	3.54	<2	0.005	<0.001	0.01	1.35	<0.02	<0.01	0.010	<0.01	<0.01	5.10	0.05	<0.001	0.11
631168	Drill Core	0.70	<0.001	0.004	0.15	0.03	<2	0.004	<0.001	0.04	1.57	<0.02	0.02	<0.001	<0.01	<0.01	24.17	0.03	<0.001	0.08
631169	Drill Core	1.35	0.002	0.013	0.44	0.24	<2	0.004	<0.001	0.04	2.40	<0.02	0.01	<0.001	<0.01	<0.01	18.93	0.35	0.001	0.11
631170	Rock	0.39	<0.001	<0.001	0.03	<0.01	<2	<0.001	<0.001	0.02	0.16	<0.02	0.01	<0.001	<0.01	<0.01	21.67	0.03	<0.001	11.05
631171	Drill Core	0.65	0.006	0.012	0.17	0.33	<2	0.009	<0.001	0.01	0.90	<0.02	0.01	0.001	<0.01	<0.01	10.67	2.31	0.004	0.10
631172	Drill Core	0.87	0.002	0.006	0.09	0.06	<2	0.003	<0.001	0.04	0.62	<0.02	0.01	<0.001	<0.01	<0.01	25.23	0.11	<0.001	0.09
631173	Drill Core	1.68	0.005	0.012	0.35	0.89	3	0.011	<0.001	0.02	2.79	<0.02	<0.01	0.003	<0.01	<0.01	11.07	0.33	0.003	0.11
631174	Drill Core	1.47	0.005	0.004	0.04	0.14	2	0.014	<0.001	0.01	1.80	<0.02	<0.01	<0.001	<0.01	<0.01	2.99	0.08	0.007	0.27
631175	Drill Core	1.21	0.007	0.009	0.04	0.08	2	0.018	<0.001	<0.01	2.69	<0.02	<0.01	<0.001	<0.01	<0.01	1.93	0.06	0.007	0.35
631176	Drill Core	0.87	0.007	0.005	0.04	0.02	3	0.017	0.001	<0.01	2.18	<0.02	<0.01	<0.001	<0.01	<0.01	0.93	0.07	0.009	0.39



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: December 13, 2010

Page: 2 of 2 **Part** 2

CERTIFICATE OF ANALYSIS

WHI10000657.1

	Method Analyte Unit MDL	7TD	7TD	7TD	7TD	G8SG	7TD.1
		Na	K	W	S	SG	Pb
		%	%	%	%		%
		0.01	0.01	0.01	0.05	0	0.02
631151	Drill Core	<0.01	2.07	<0.01	1.47	2.33	
631152	Drill Core	0.07	0.63	<0.01	12.88	2.77	
631153	Drill Core	0.09	1.52	<0.01	7.40	2.50	
631154	Drill Core	<0.01	2.28	<0.01	1.63	2.29	
631155	Drill Core	<0.01	0.96	<0.01	0.94	2.41	
631156	Drill Core	<0.01	0.62	<0.01	0.55	2.46	
631157	Drill Core	<0.01	0.78	<0.01	1.38	2.44	
631158	Drill Core	<0.01	0.17	<0.01	0.32	2.46	
631159	Drill Core	<0.01	0.15	<0.01	6.63	2.63	
631160	Drill Core	<0.01	0.19	<0.01	2.34	2.49	
631161	Drill Core	<0.01	0.19	<0.01	2.54	2.51	
631162	Drill Core	<0.01	0.36	<0.01	8.77	2.61	
631163	Drill Core	<0.01	0.34	<0.01	6.94	2.68	
631164	Drill Core	<0.01	0.13	<0.01	12.43	3.08	11.35
631165	Drill Core	<0.01	0.02	<0.01	13.27	3.28	
631166	Drill Core	<0.01	0.13	<0.01	13.64	3.02	
631167	Drill Core	<0.01	0.37	<0.01	3.14	2.54	
631168	Drill Core	<0.01	0.17	<0.01	1.74	2.49	
631169	Drill Core	<0.01	0.20	<0.01	2.82	2.54	
631170	Rock	<0.01	0.05	<0.01	<0.05	2.65	
631171	Drill Core	<0.01	0.43	<0.01	0.90	2.39	
631172	Drill Core	<0.01	0.13	<0.01	0.69	2.45	
631173	Drill Core	<0.01	0.48	<0.01	3.52	2.42	
631174	Drill Core	<0.01	2.24	<0.01	1.73	2.33	
631175	Drill Core	<0.01	2.97	<0.01	2.86	2.31	
631176	Drill Core	<0.01	3.48	<0.01	2.26	2.21	



Acme Analytical Laboratories (Vancouver) Ltd.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: **Selwyn Resources Ltd.**

Suite 700 - 509 Richards Street

Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: December 13, 2010

Page: 1 of 1 Part 1

QUALITY CONTROL REPORT

WHI10000657.1

	Method Analyte Unit MDL	WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD
		Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg	Al
		kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%	%
		0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01	0.01
Pulp Duplicates																					
631173	Drill Core	1.68	0.005	0.012	0.35	0.89	3	0.011	<0.001	0.02	2.79	<0.02	<0.01	0.003	<0.01	<0.01	11.07	0.33	0.003	0.11	0.80
REP 631173	QC		0.005	0.012	0.35	0.88	3	0.011	<0.001	0.02	2.81	<0.02	<0.01	0.003	<0.01	<0.01	10.96	0.34	0.002	0.11	0.79
Reference Materials																					
STD CCU-1C	Standard																				
STD CZN-3	Standard																				
STD OREAS131A	Standard		<0.001	0.033	1.78	2.93	31	0.003	0.002	0.18	5.86	<0.02	<0.01	0.008	<0.01	<0.01	5.40	0.05	0.002	3.20	4.75
STD PTC-1A	Standard																				
STD R4T	Standard		0.065	0.516	1.62	3.47	88	0.359	0.041	0.09	24.29	<0.02	0.02	0.019	0.02	<0.01	2.23	0.04	0.018	1.45	4.06
STD SARM 71	Standard																				
STD SU-1B	Standard		<0.001	1.191	0.03	0.03	7	1.973	0.067	0.07	25.51	<0.02	0.03	<0.001	<0.01	<0.01	2.28	0.06	0.031	1.82	4.49
STD R4T Expected			0.062	0.502	1.518	3.376	86	0.339	0.039	0.086	24.07	0.0087	0.0185	0.018	0.0138	0.0018	2.166	0.045	0.018	1.384	3.897
STD OREAS131A Expected			0.001	0.0322	1.72	2.83	30.9	0.0027	0.0023	0.1722	5.8166	0.0082	0.0028	0.0081	0.0047	0.001	5.286	0.0536	0.0025	3.1182	4.6057
STD SU-1B Expected			0.0004	1.185	0.0058	0.0235	6.4	1.97	0.0672	0.0703	25.54	0.00025	0.03	0.0003	0.00002	0.0003	2.21	0.06	0.032	1.79	4.39
STD CZN-3 Expected																					
STD CCU-1C Expected																					
STD PTC-1A Expected																					
BLK	Blank		<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	<0.01	<0.01	<0.02	<0.01	<0.001	<0.01	<0.01	<0.01	<0.01	<0.001	<0.01	<0.01
BLK	Blank																				
Prep Wash																					
G1	Prep Blank		<0.001	<0.001	0.03	0.01	<2	<0.001	<0.001	0.08	2.40	<0.02	0.07	<0.001	<0.01	<0.01	2.43	0.08	<0.001	0.64	7.56
G1	Prep Blank		<0.001	<0.001	0.03	<0.01	<2	<0.001	<0.001	0.08	2.45	<0.02	0.07	<0.001	<0.01	<0.01	2.41	0.08	<0.001	0.64	7.52



Acme Analytical Laboratories (Vancouver) Ltd.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: Selwyn Resources Ltd.

Suite 700 - 509 Richards Street

Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: December 13, 2010

Page: 1 of 1 **Part** 2

QUALITY CONTROL REPORT

WHI10000657.1

Method		7TD	7TD	7TD	7TD	G8SG	7TD.1
Analyte		Na	K	W	S	SG	Pb
Unit		%	%	%	%		%
MDL		0.01	0.01	0.01	0.05	0	0.02
Pulp Duplicates							
631173	Drill Core	<0.01	0.48	<0.01	3.52	2.42	
REP 631173	QC	<0.01	0.48	<0.01	3.54		
Reference Materials							
STD CCU-1C	Standard						0.41
STD CZN-3	Standard						0.13
STD OREAS131A	Standard	0.16	3.45	<0.01	4.77		
STD PTC-1A	Standard						0.05
STD R4T	Standard	0.92	1.19	<0.01	12.71		
STD SARM 71	Standard						<0.02
STD SU-1B	Standard	1.73	0.62	<0.01	8.25		
STD R4T Expected		0.9	1.153	0.00016	12.9903		
STD OREAS131A Expected		0.1501	3.1584	0.0005	4.8		
STD SU-1B Expected		1.662	0.6	0.0007	8.76		
STD CZN-3 Expected							0.113
STD CCU-1C Expected							0.34
STD PTC-1A Expected							0.05
BLK	Blank	<0.01	<0.01	<0.01	<0.05		
BLK	Blank						<0.02
Prep Wash							
G1	Prep Blank	2.73	3.00	<0.01	<0.05	2.72	
G1	Prep Blank	2.70	2.97	<0.01	<0.05	2.72	



1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: Selwyn Resources Ltd.

Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Submitted By: Jason K. Dunning

Receiving Lab: Canada-Whitehorse

Received: November 16, 2010

Report Date: November 30, 2010

Page: 1 of 2

CERTIFICATE OF ANALYSIS

WHI10000656.1

CLIENT JOB INFORMATION

Project: Selwyn Project
Shipment ID:
P.O. Number: 1052
Number of Samples: 20

SAMPLE DISPOSAL

STOR-PLP Store After 90 days Invoice for Storage
STOR-RJT Store After 90 days Invoice for Storage

Acme does not accept responsibility for samples left at the laboratory after 90 days without prior written instructions for sample storage or return.

Invoice To: Selwyn Resources Ltd.
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6
Canada

CC:

SAMPLE PREPARATION AND ANALYTICAL PROCEDURES

Method Code	Number of Samples	Code Description	Test Wgt (g)	Report Status	Lab
R200-250	20	Crush split and pulverize 250g drill core to 200 mesh			WHI
7TD2	20	4 Acid digestion ICP-ES analysis.	0.5	Completed	VAN
G812	20	Specific Gravity on Pulp		Completed	VAN

ADDITIONAL COMMENTS



This report supersedes all previous preliminary and final reports with this file number dated prior to the date on this certificate. Signature indicates final approval; preliminary reports are unsigned and should be used for reference only.
All results are considered the confidential property of the client. Acme assumes the liabilities for actual cost of analysis only.
** asterisk indicates that an analytical result could not be provided due to unusually high levels of interference from other elements.



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**

Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: November 30, 2010

Page: 2 of 2 Part 1

CERTIFICATE OF ANALYSIS

WHI10000656.1

	Method Analyte Unit MDL	WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	
		Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg	Al
		kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%	%
		0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01	0.01
632851	Drill Core	0.70	<0.001	0.005	0.07	0.01	<2	0.011	<0.001	<0.01	1.40	<0.02	0.01	<0.001	<0.01	<0.01	8.18	2.60	0.009	0.85	3.95
632852	Drill Core	1.33	<0.001	0.009	0.86	7.80	6	0.004	<0.001	0.02	3.78	<0.02	0.02	0.022	<0.01	<0.01	12.99	0.10	0.002	0.16	0.57
632853	Drill Core	1.46	<0.001	0.012	2.36	9.51	7	0.006	<0.001	0.02	3.89	<0.02	<0.01	0.027	<0.01	<0.01	7.08	0.14	0.003	0.28	0.95
632854	Drill Core	0.49	<0.001	0.005	0.09	0.80	<2	0.012	<0.001	<0.01	1.46	<0.02	<0.01	0.002	<0.01	<0.01	4.32	1.59	0.008	0.72	3.89
632855	Drill Core	1.28	0.001	0.004	0.06	0.22	<2	0.007	<0.001	<0.01	0.67	<0.02	<0.01	<0.001	<0.01	<0.01	2.51	0.41	0.002	0.13	1.19
632856	Drill Core	1.34	<0.001	0.006	0.02	0.08	2	0.005	<0.001	0.04	0.72	<0.02	<0.01	<0.001	<0.01	<0.01	11.47	0.37	0.002	0.12	0.77
632857	Drill Core	0.83	0.002	0.007	2.89	8.57	4	0.007	<0.001	0.03	8.26	<0.02	<0.01	0.041	<0.01	<0.01	9.20	0.08	0.002	0.10	0.83
632858	Drill Core	1.44	0.003	0.005	0.53	3.16	<2	0.007	<0.001	0.02	3.49	<0.02	<0.01	0.009	<0.01	<0.01	7.28	0.06	0.002	0.07	0.77
632859	Drill Core	0.97	0.001	0.004	2.05	9.97	3	0.004	<0.001	0.03	1.73	<0.02	<0.01	0.028	<0.01	<0.01	14.64	0.07	0.001	0.08	0.60
632860	Drill Core	0.59	0.002	0.004	1.16	4.98	<2	0.006	<0.001	0.03	2.34	<0.02	<0.01	0.014	<0.01	<0.01	11.49	0.05	0.002	0.09	0.76
632861	Drill Core	0.60	0.002	0.004	1.05	4.68	2	0.007	<0.001	0.02	2.48	<0.02	<0.01	0.012	<0.01	<0.01	9.49	0.05	0.001	0.09	0.82
632862	Drill Core	0.72	0.003	0.007	2.80	11.13	3	0.007	<0.001	0.02	1.57	<0.02	<0.01	0.035	<0.01	<0.01	11.39	0.13	0.002	0.11	0.91
632863	Drill Core	1.93	<0.001	0.003	0.15	0.07	<2	0.004	<0.001	0.04	1.96	<0.02	<0.01	<0.001	<0.01	<0.01	15.38	0.05	0.002	0.09	0.58
632864	Drill Core	2.14	<0.001	<0.001	0.43	0.03	<2	0.002	<0.001	0.04	0.21	<0.02	0.02	<0.001	<0.01	<0.01	32.57	0.03	<0.001	0.10	0.37
632865	Drill Core	2.04	<0.001	0.003	0.05	0.04	<2	0.004	<0.001	0.04	0.69	<0.02	0.02	<0.001	<0.01	<0.01	27.11	0.04	0.001	0.11	0.57
632866	Drill Core	1.71	<0.001	0.004	0.09	0.04	<2	0.005	<0.001	0.04	3.35	<0.02	0.01	<0.001	<0.01	<0.01	14.67	0.03	0.001	0.12	0.73
632867	Drill Core	0.95	0.003	0.004	<0.02	<0.01	<2	0.012	<0.001	0.03	2.03	<0.02	0.01	<0.001	<0.01	<0.01	12.67	0.09	0.009	0.35	3.80
632868	Drill Core	0.25	<0.001	0.004	<0.02	<0.01	<2	0.010	<0.001	0.02	1.86	<0.02	<0.01	<0.001	<0.01	<0.01	6.96	0.09	0.009	0.48	4.34
632869	Drill Core	0.49	<0.001	0.005	<0.02	<0.01	<2	0.008	<0.001	0.05	3.18	<0.02	0.02	<0.001	<0.01	<0.01	20.22	0.05	0.006	0.44	3.73
632870	Rock	0.34	<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	0.02	0.43	<0.02	0.01	<0.001	<0.01	<0.01	20.21	0.03	<0.001	11.24	0.37



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**

Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: November 30, 2010

Page: 2 of 2 **Part** 2

CERTIFICATE OF ANALYSIS

WHI10000656.1

	Method	7TD	7TD	7TD	7TD	G8SG
	Analyte	Na	K	W	S	SG
	Unit	%	%	%	%	
	MDL	0.01	0.01	0.01	0.05	0
632851	Drill Core	0.02	2.49	<0.01	1.33	2.16
632852	Drill Core	<0.01	0.33	<0.01	8.66	2.65
632853	Drill Core	<0.01	0.55	<0.01	9.65	2.69
632854	Drill Core	0.02	2.48	<0.01	1.81	2.13
632855	Drill Core	<0.01	0.67	<0.01	0.70	2.32
632856	Drill Core	0.02	0.49	<0.01	0.77	2.46
632857	Drill Core	<0.01	0.48	<0.01	14.02	2.67
632858	Drill Core	<0.01	0.47	<0.01	5.69	2.43
632859	Drill Core	<0.01	0.30	<0.01	7.37	2.62
632860	Drill Core	<0.01	0.42	<0.01	5.47	2.45
632861	Drill Core	<0.01	0.45	<0.01	5.40	2.40
632862	Drill Core	<0.01	0.51	<0.01	7.78	2.53
632863	Drill Core	<0.01	0.29	<0.01	2.21	2.38
632864	Drill Core	<0.01	0.17	<0.01	0.26	2.45
632865	Drill Core	<0.01	0.28	<0.01	0.72	2.40
632866	Drill Core	<0.01	0.39	<0.01	3.81	2.52
632867	Drill Core	0.01	2.29	<0.01	2.13	2.22
632868	Drill Core	0.01	2.95	<0.01	1.69	2.32
632869	Drill Core	<0.01	2.09	<0.01	3.21	2.32
632870	Rock	0.03	0.03	<0.01	0.06	2.64



Acme Analytical Laboratories (Vancouver) Ltd.
1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: November 30, 2010

Page: 1 of 1 Part 1

QUALITY CONTROL REPORT

WHI10000656.1

	Method Analyte Unit MDL	WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD
		Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg	Al
		kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%	%
		0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01	0.01
Pulp Duplicates																					
632860	Drill Core	0.59	0.002	0.004	1.16	4.98	<2	0.006	<0.001	0.03	2.34	<0.02	<0.01	0.014	<0.01	<0.01	11.49	0.05	0.002	0.09	0.76
REP 632860	QC		0.002	0.004	1.12	4.91	<2	0.006	<0.001	0.03	2.29	<0.02	<0.01	0.013	<0.01	<0.01	11.33	0.05	0.001	0.09	0.74
Core Reject Duplicates																					
632865	Drill Core	2.04	<0.001	0.003	0.05	0.04	<2	0.004	<0.001	0.04	0.69	<0.02	0.02	<0.001	<0.01	<0.01	27.11	0.04	0.001	0.11	0.57
DUP 632865	QC		<0.001	0.003	0.05	0.04	<2	0.004	<0.001	0.04	0.70	<0.02	0.02	<0.001	<0.01	<0.01	26.81	0.04	0.001	0.11	0.57
Reference Materials																					
STD OREAS131A	Standard		<0.001	0.032	1.72	2.90	32	0.003	0.002	0.17	5.77	<0.02	<0.01	0.008	<0.01	<0.01	5.35	0.06	0.002	3.17	4.70
STD R4T	Standard		0.060	0.505	1.50	3.46	87	0.354	0.039	0.09	24.15	<0.02	0.02	0.018	0.01	<0.01	2.21	0.05	0.018	1.44	3.98
STD SU-1B	Standard		<0.001	1.179	<0.02	0.03	6	1.989	0.065	0.07	25.19	<0.02	0.03	<0.001	<0.01	<0.01	2.24	0.06	0.031	1.81	4.44
STD R4T Expected			0.062	0.502	1.518	3.376	86	0.339	0.039	0.086	24.07	0.0087	0.0185	0.018	0.0138	0.0018	2.166	0.045	0.018	1.384	3.897
STD OREAS131A Expected			0.001	0.0322	1.72	2.83	30.9	0.0027	0.0023	0.1722	5.8166	0.0082	0.0028	0.0081	0.0047	0.001	5.286	0.0536	0.0025	3.1182	4.6057
STD SU-1B Expected			0.0004	1.185	0.0058	0.0235	6.4	1.97	0.0672	0.0703	25.54	0.00025	0.03	0.0003	0.00002	0.0003	2.21	0.06	0.032	1.79	4.39
BLK	Blank		<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	<0.01	<0.01	<0.02	<0.01	<0.001	<0.01	<0.01	<0.01	<0.01	<0.001	<0.01	<0.01
Prep Wash																					
G1	Prep Blank		<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	0.07	2.31	<0.02	0.08	<0.001	<0.01	<0.01	2.40	0.08	<0.001	0.62	7.86
G1	Prep Blank		<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	0.07	2.30	<0.02	0.07	<0.001	<0.01	<0.01	2.47	0.08	<0.001	0.63	7.61



Acme Analytical Laboratories (Vancouver) Ltd.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: **Selwyn Resources Ltd.**

Suite 700 - 509 Richards Street

Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: November 30, 2010

Page: 1 of 1 **Part** 2

QUALITY CONTROL REPORT

WHI10000656.1

		Method	7TD	7TD	7TD	7TD	G8SG
		Analyte	Na	K	W	S	SG
		Unit	%	%	%	%	
		MDL	0.01	0.01	0.01	0.05	0
Pulp Duplicates							
632860	Drill Core		<0.01	0.42	<0.01	5.47	2.45
REP 632860	QC		<0.01	0.41	<0.01	5.37	
Core Reject Duplicates							
632865	Drill Core		<0.01	0.28	<0.01	0.72	2.40
DUP 632865	QC		<0.01	0.29	<0.01	0.75	2.40
Reference Materials							
STD OREAS131A	Standard		0.15	3.39	<0.01	4.83	
STD R4T	Standard		0.93	1.18	<0.01	12.60	
STD SU-1B	Standard		1.70	0.60	<0.01	8.80	
STD R4T Expected			0.9	1.153	0.00016	12.9903	
STD OREAS131A Expected			0.1501	3.1584	0.0005	4.8	
STD SU-1B Expected			1.662	0.6	0.0007	8.76	
BLK	Blank		<0.01	<0.01	<0.01	<0.05	
Prep Wash							
G1	Prep Blank		2.79	2.60	<0.01	<0.05	2.66
G1	Prep Blank		2.75	2.58	<0.01	<0.05	2.66



1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: Selwyn Resources Ltd.

Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Submitted By: Jason K. Dunning

Receiving Lab: Canada-Whitehorse

Received: November 16, 2010

Report Date: December 03, 2010

Page: 1 of 5

CERTIFICATE OF ANALYSIS

WHI10000655.1

CLIENT JOB INFORMATION

Project: Selwyn Project
Shipment ID:
P.O. Number 1050
Number of Samples: 104

SAMPLE DISPOSAL

STOR-PLP Store After 90 days Invoice for Storage
STOR-RJT Store After 90 days Invoice for Storage

Acme does not accept responsibility for samples left at the laboratory after 90 days without prior written instructions for sample storage or return.

Invoice To: Selwyn Resources Ltd.
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6
Canada

CC:

SAMPLE PREPARATION AND ANALYTICAL PROCEDURES

Method Code	Number of Samples	Code Description	Test Wgt (g)	Report Status	Lab
7TD.1	9	4 Acid digestion ICP-ES analysis	0.1	Completed	VAN
R200-250	104	Crush split and pulverize 250g drill core to 200 mesh			WHI
7TD2	104	4 Acid digestion ICP-ES analysis.	0.5	Completed	VAN
G812	104	Specific Gravity on Pulp		Completed	VAN

ADDITIONAL COMMENTS



This report supersedes all previous preliminary and final reports with this file number dated prior to the date on this certificate. Signature indicates final approval; preliminary reports are unsigned and should be used for reference only.
All results are considered the confidential property of the client. Acme assumes the liabilities for actual cost of analysis only.
** asterisk indicates that an analytical result could not be provided due to unusually high levels of interference from other elements.



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: December 03, 2010

Page: 2 of 5 Part 1

CERTIFICATE OF ANALYSIS

WHI10000655.1

	Method Analyte Unit MDL	7TD.1	WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD
		Pb	Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg
		%	kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%
		0.02	0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01
632651	Drill Core		3.11	0.001	0.003	0.02	0.87	<2	0.010	<0.001	<0.01	0.84	<0.02	<0.01	0.003	<0.01	<0.01	1.90	0.81	0.005	0.15
632652	Drill Core		2.40	0.004	0.003	0.31	0.51	<2	0.008	<0.001	<0.01	1.05	<0.02	<0.01	0.003	<0.01	<0.01	0.83	0.08	0.003	0.11
632653	Drill Core		1.29	0.004	0.012	2.85	9.04	3	0.007	<0.001	0.03	4.54	<0.02	<0.01	0.052	<0.01	<0.01	2.65	0.03	0.002	0.09
632654	Drill Core		0.43	<0.001	<0.001	0.22	0.05	<2	0.003	<0.001	0.07	0.88	<0.02	0.02	<0.001	<0.01	<0.01	34.71	0.02	<0.001	0.12
632655	Drill Core		0.38	0.011	0.016	3.04	12.46	5	0.022	0.001	0.02	8.48	<0.02	<0.01	0.043	<0.01	<0.01	0.52	0.10	0.007	0.29
632656	Drill Core		0.66	0.004	0.009	1.79	10.44	3	0.007	<0.001	0.04	4.04	<0.02	<0.01	0.039	<0.01	<0.01	9.66	0.04	0.002	0.12
632657	Drill Core		1.51	0.003	0.011	2.21	10.67	3	0.008	<0.001	0.02	6.75	<0.02	<0.01	0.041	<0.01	<0.01	1.55	0.04	0.003	0.08
632658	Drill Core		1.42	0.001	0.002	0.32	1.10	<2	0.003	<0.001	0.07	1.75	<0.02	0.02	0.004	<0.01	0.01	29.48	0.02	<0.001	0.09
632659	Drill Core		1.18	0.004	0.008	0.93	6.09	2	0.010	<0.001	0.02	5.05	<0.02	<0.01	0.015	<0.01	0.01	3.77	0.07	0.003	0.11
632660	Drill Core		1.12	0.002	0.004	0.49	3.80	<2	0.005	<0.001	0.03	1.84	<0.02	0.01	0.010	<0.01	<0.01	17.07	0.05	0.002	0.11
632661	Drill Core		1.18	0.002	0.004	0.37	3.70	<2	0.005	<0.001	0.03	2.11	<0.02	0.01	0.010	<0.01	<0.01	17.06	0.06	0.002	0.11
632662	Drill Core		1.68	0.002	0.001	0.06	0.75	<2	0.005	<0.001	0.02	0.67	<0.02	0.01	0.002	<0.01	<0.01	15.09	0.05	0.001	0.07
632663	Drill Core		1.57	0.001	<0.001	<0.02	0.29	<2	0.003	<0.001	0.02	0.44	<0.02	<0.01	<0.001	<0.01	<0.01	11.51	0.04	<0.001	0.04
632664	Drill Core		0.41	<0.001	0.002	<0.02	2.15	<2	0.002	<0.001	<0.01	0.72	<0.02	<0.01	0.008	<0.01	<0.01	2.98	0.02	<0.001	0.03
632665	Drill Core		0.43	<0.001	<0.001	<0.02	<0.01	<2	0.002	<0.001	<0.01	0.36	<0.02	<0.01	<0.001	<0.01	<0.01	5.41	0.02	<0.001	0.03
632666	Drill Core		2.15	0.001	0.001	<0.02	0.11	<2	0.003	<0.001	<0.01	0.75	<0.02	<0.01	<0.001	<0.01	<0.01	2.08	0.03	<0.001	0.05
632667	Drill Core		1.63	0.002	0.001	0.02	0.72	<2	0.006	<0.001	<0.01	0.66	<0.02	<0.01	0.002	<0.01	<0.01	2.92	0.04	0.002	0.06
632668	Drill Core		1.70	0.006	0.002	<0.02	0.58	<2	0.012	<0.001	<0.01	1.44	<0.02	<0.01	0.002	<0.01	<0.01	0.14	0.03	0.002	0.11
632669	Drill Core		0.70	0.003	0.002	<0.02	1.48	<2	0.010	<0.001	<0.01	0.82	<0.02	<0.01	0.005	<0.01	<0.01	0.31	0.03	0.001	0.12
632670	Rock		0.39	<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	0.01	0.29	<0.02	0.01	<0.001	<0.01	<0.01	21.14	0.04	<0.001	11.20
632671	Drill Core		1.31	0.004	0.002	<0.02	0.66	<2	0.010	<0.001	<0.01	1.05	<0.02	<0.01	0.002	<0.01	<0.01	1.80	0.06	0.004	0.11
632672	Drill Core		0.73	<0.001	0.001	<0.02	0.18	<2	0.003	<0.001	0.02	0.77	<0.02	0.01	<0.001	<0.01	<0.01	18.69	0.03	<0.001	0.05
632673	Drill Core		1.60	0.005	0.003	0.06	1.22	<2	0.011	<0.001	0.01	1.88	<0.02	<0.01	0.004	<0.01	<0.01	3.63	0.05	0.002	0.13
632674	Drill Core		2.41	0.005	0.003	0.05	0.89	<2	0.012	<0.001	<0.01	2.00	<0.02	<0.01	0.003	<0.01	<0.01	1.07	0.07	0.002	0.13
632675	Drill Core		0.51	0.004	0.003	0.43	2.94	<2	0.011	<0.001	0.01	1.16	<0.02	<0.01	0.010	<0.01	<0.01	3.25	0.05	0.002	0.11
632676	Drill Core		0.83	0.011	0.004	0.13	0.21	<2	0.017	0.001	0.02	2.40	<0.02	<0.01	<0.001	<0.01	<0.01	6.43	0.07	0.004	0.19
632677	Drill Core	13.52	0.72	0.008	0.016	>10	4.41	6	0.021	0.001	0.01	7.57	<0.02	<0.01	0.016	<0.01	<0.01	0.82	0.08	0.007	0.17
632678	Drill Core		1.80	0.011	0.006	0.34	1.68	<2	0.019	0.001	0.01	4.45	<0.02	<0.01	0.006	<0.01	<0.01	4.41	0.09	0.004	0.20
632679	Drill Core		0.87	0.009	0.003	0.04	1.12	<2	0.017	0.001	<0.01	1.73	<0.02	<0.01	0.004	<0.01	<0.01	1.60	0.08	0.005	0.18
632680	Rock Pulp		0.02	<0.001	0.495	1.44	4.35	28	0.001	0.002	0.74	5.65	<0.02	0.01	0.029	<0.01	<0.01	4.33	0.05	0.003	1.61



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**

Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: December 03, 2010

Page: 2 of 5 Part 2

CERTIFICATE OF ANALYSIS

WHI10000655.1

	Method Analyte Unit MDL	7TD	7TD	7TD	7TD	7TD	G8SG
		Al	Na	K	W	S	SG
		%	%	%	%	%	
		0.01	0.01	0.01	0.01	0.05	0
632651	Drill Core	1.67	0.02	1.05	<0.01	1.29	2.34
632652	Drill Core	1.23	<0.01	0.77	<0.01	1.32	2.32
632653	Drill Core	0.96	<0.01	0.56	<0.01	9.98	2.72
632654	Drill Core	0.43	0.01	0.26	<0.01	1.46	2.49
632655	Drill Core	2.82	<0.01	1.66	<0.01	16.28	2.56
632656	Drill Core	1.04	<0.01	0.58	<0.01	10.21	2.57
632657	Drill Core	0.90	<0.01	0.53	<0.01	13.14	2.68
632658	Drill Core	0.32	<0.01	0.18	<0.01	3.03	2.54
632659	Drill Core	1.23	<0.01	0.73	<0.01	9.01	2.47
632660	Drill Core	0.66	<0.01	0.37	<0.01	4.31	2.45
632661	Drill Core	0.69	<0.01	0.38	<0.01	4.47	2.43
632662	Drill Core	0.55	<0.01	0.28	<0.01	1.19	2.35
632663	Drill Core	0.32	<0.01	0.16	<0.01	0.60	2.41
632664	Drill Core	0.26	<0.01	0.13	<0.01	1.68	2.51
632665	Drill Core	0.29	<0.01	0.14	<0.01	0.22	2.47
632666	Drill Core	0.45	<0.01	0.22	<0.01	0.65	2.46
632667	Drill Core	0.53	<0.01	0.28	<0.01	0.87	2.38
632668	Drill Core	1.16	<0.01	0.79	<0.01	1.79	2.21
632669	Drill Core	0.99	<0.01	0.58	<0.01	1.48	2.27
632670	Rock	0.33	<0.01	0.09	<0.01	0.21	2.69
632671	Drill Core	1.31	<0.01	0.79	<0.01	1.33	2.33
632672	Drill Core	0.31	<0.01	0.18	<0.01	1.07	2.50
632673	Drill Core	1.28	<0.01	0.76	<0.01	2.78	2.34
632674	Drill Core	1.41	<0.01	0.90	<0.01	2.63	2.28
632675	Drill Core	1.26	<0.01	0.81	<0.01	2.75	2.30
632676	Drill Core	2.32	<0.01	1.48	<0.01	2.95	2.08
632677	Drill Core	1.94	<0.01	1.15	<0.01	12.84	2.65
632678	Drill Core	2.43	<0.01	1.47	<0.01	6.19	2.24
632679	Drill Core	2.28	<0.01	1.50	<0.01	2.57	2.09
632680	Rock Pulp	4.61	0.10	3.54	<0.01	5.56	N.A.



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: December 03, 2010

Page: 3 of 5 Part 1

CERTIFICATE OF ANALYSIS

WHI10000655.1

	Method Analyte Unit MDL	7TD.1	WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD
		Pb	Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg
		%	kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%
		0.02	0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01
632681	Drill Core		0.45	<0.001	0.003	0.03	0.37	<2	0.005	<0.001	0.04	3.17	<0.02	0.01	0.001	<0.01	<0.01	26.69	0.02	<0.001	0.08
632682	Drill Core		2.71	0.007	0.003	0.50	0.85	<2	0.014	<0.001	<0.01	1.79	<0.02	<0.01	0.003	<0.01	<0.01	0.70	0.05	0.002	0.13
632683	Drill Core		0.93	0.011	0.003	0.04	0.09	<2	0.014	<0.001	<0.01	1.34	<0.02	<0.01	<0.001	<0.01	<0.01	0.45	0.04	0.003	0.15
632684	Drill Core		2.65	0.006	0.015	1.39	9.24	2	0.011	<0.001	0.04	8.70	<0.02	<0.01	0.026	<0.01	<0.01	4.38	0.04	0.002	0.09
632685	Drill Core		3.07	<0.001	<0.001	0.32	0.25	<2	<0.001	<0.001	0.07	1.18	<0.02	0.02	<0.001	<0.01	<0.01	35.82	0.03	<0.001	0.11
632686	Drill Core		1.83	0.002	0.008	1.24	7.78	<2	0.006	<0.001	0.04	5.46	<0.02	<0.01	0.022	<0.01	<0.01	8.13	0.07	<0.001	0.06
632687	Drill Core		0.53	<0.001	0.002	0.11	1.04	<2	0.001	<0.001	0.06	1.11	<0.02	0.01	0.003	<0.01	<0.01	29.99	0.01	<0.001	0.10
632688	Drill Core	18.41	0.52	<0.001	0.005	>10	3.83	4	0.003	<0.001	0.03	2.62	<0.02	<0.01	0.011	<0.01	<0.01	6.82	0.02	<0.001	0.04
632689	Drill Core		0.77	<0.001	0.001	1.00	2.61	<2	0.001	<0.001	0.06	2.13	<0.02	0.02	0.009	<0.01	<0.01	32.39	0.05	<0.001	0.08
632690	Drill Core		1.06	<0.001	<0.001	0.36	0.74	<2	<0.001	<0.001	0.08	0.36	<0.02	0.02	0.003	<0.01	<0.01	37.41	0.02	<0.001	0.11
632691	Drill Core		1.23	<0.001	<0.001	0.39	0.83	<2	<0.001	<0.001	0.08	0.40	<0.02	0.02	0.003	<0.01	<0.01	36.85	0.03	<0.001	0.11
632692	Drill Core		3.05	<0.001	<0.001	0.35	0.40	<2	0.001	<0.001	0.06	1.97	<0.02	0.01	0.001	<0.01	<0.01	29.09	0.02	<0.001	0.09
632693	Drill Core		1.55	<0.001	0.001	1.16	2.25	<2	0.001	<0.001	0.07	0.76	<0.02	0.02	0.008	<0.01	<0.01	32.24	0.06	<0.001	0.11
632694	Drill Core		2.57	<0.001	0.001	0.14	0.59	<2	0.004	<0.001	0.01	2.29	<0.02	<0.01	0.002	<0.01	<0.01	6.05	0.11	<0.001	0.08
632695	Drill Core		2.01	<0.001	0.002	1.12	4.55	<2	0.002	<0.001	0.05	1.47	<0.02	0.01	0.015	<0.01	<0.01	29.81	0.07	<0.001	0.08
632696	Drill Core		2.28	<0.001	<0.001	0.45	0.94	<2	0.001	<0.001	0.05	5.33	<0.02	0.02	0.003	<0.01	<0.01	30.97	0.06	<0.001	0.09
632697	Drill Core		3.27	<0.001	0.001	0.95	2.14	<2	0.002	<0.001	0.06	2.53	<0.02	0.01	0.008	<0.01	<0.01	30.39	0.06	<0.001	0.09
632698	Drill Core		2.23	<0.001	0.001	0.55	0.83	<2	0.003	<0.001	0.05	1.79	<0.02	0.01	0.003	<0.01	<0.01	34.28	0.02	<0.001	0.08
632699	Drill Core		0.40	0.003	0.009	3.36	13.13	4	0.007	<0.001	0.04	6.08	<0.02	<0.01	0.037	<0.01	<0.01	10.26	0.08	0.001	0.11
632700	Rock		0.34	<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	0.02	0.32	<0.02	0.01	<0.001	<0.01	<0.01	21.26	0.04	0.002	10.95
632701	Drill Core		1.66	<0.001	<0.001	1.18	1.12	<2	0.002	<0.001	0.06	1.39	<0.02	0.02	0.004	<0.01	<0.01	31.86	0.03	<0.001	0.08
632702	Drill Core		1.27	0.001	0.005	4.30	13.56	4	0.003	<0.001	0.04	3.46	<0.02	0.01	0.043	<0.01	<0.01	15.53	0.06	<0.001	0.08
632703	Drill Core		0.48	0.002	0.004	3.36	7.35	3	0.004	<0.001	0.06	3.91	<0.02	0.01	0.023	<0.01	<0.01	22.28	0.07	0.002	0.11
632704	Drill Core		2.01	<0.001	0.002	2.19	4.67	<2	0.003	<0.001	0.04	1.82	<0.02	0.01	0.016	<0.01	<0.01	21.97	0.06	0.001	0.11
632705	Drill Core		0.66	0.001	0.003	0.47	3.71	<2	0.008	<0.001	0.02	1.90	<0.02	<0.01	0.012	<0.01	<0.01	3.75	0.09	0.002	0.17
632706	Drill Core		2.60	0.001	0.002	0.93	3.25	<2	0.003	<0.001	0.04	2.79	<0.02	0.01	0.010	<0.01	<0.01	24.73	0.05	0.001	0.09
632707	Drill Core		1.36	0.002	0.004	1.49	6.32	2	0.004	<0.001	0.04	4.06	<0.02	0.01	0.019	<0.01	<0.01	19.55	0.05	0.001	0.09
632708	Drill Core		0.96	0.002	0.003	1.39	2.81	<2	0.006	<0.001	0.03	2.00	<0.02	<0.01	0.008	<0.01	<0.01	12.17	0.04	0.002	0.11
632709	Drill Core		1.20	<0.001	<0.001	1.36	0.43	<2	0.002	<0.001	0.03	0.78	<0.02	0.02	0.001	<0.01	<0.01	29.84	0.02	<0.001	0.08
632710	Rock Pulp		0.02	0.001	0.815	0.91	1.34	222	0.002	0.002	0.22	2.68	<0.02	0.01	0.009	0.04	<0.01	1.92	<0.01	0.003	0.12



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: Selwyn Resources Ltd.
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: December 03, 2010

Page: 3 of 5 **Part** 2

CERTIFICATE OF ANALYSIS

WHI10000655.1

	Method Analyte Unit MDL	7TD	7TD	7TD	7TD	7TD	G8SG
		Al	Na	K	W	S	SG
		%	%	%	%	%	
		0.01	0.01	0.01	0.01	0.05	0
632681	Drill Core	0.27	<0.01	0.16	<0.01	4.21	2.54
632682	Drill Core	1.73	<0.01	1.16	<0.01	2.57	2.20
632683	Drill Core	2.28	<0.01	1.66	<0.01	1.58	2.16
632684	Drill Core	1.04	<0.01	0.68	<0.01	15.33	2.66
632685	Drill Core	0.06	<0.01	0.03	<0.01	2.00	2.53
632686	Drill Core	0.51	<0.01	0.29	<0.01	10.78	2.59
632687	Drill Core	0.07	<0.01	0.03	<0.01	2.15	2.51
632688	Drill Core	0.22	<0.01	0.11	<0.01	7.91	2.95
632689	Drill Core	0.16	<0.01	0.07	<0.01	4.47	2.61
632690	Drill Core	0.05	<0.01	0.02	<0.01	1.18	2.47
632691	Drill Core	0.05	<0.01	0.02	<0.01	1.27	2.52
632692	Drill Core	0.09	<0.01	0.04	<0.01	2.91	2.56
632693	Drill Core	0.25	0.02	0.12	<0.01	2.54	2.54
632694	Drill Core	0.54	<0.01	0.28	<0.01	2.91	2.47
632695	Drill Core	0.33	<0.01	0.15	<0.01	4.66	2.56
632696	Drill Core	0.14	<0.01	0.06	<0.01	7.60	2.69
632697	Drill Core	0.20	<0.01	0.09	<0.01	4.75	2.64
632698	Drill Core	0.08	<0.01	0.03	<0.01	2.99	2.56
632699	Drill Core	0.58	<0.01	0.29	<0.01	14.72	2.80
632700	Rock	0.34	0.04	0.07	<0.01	0.22	2.61
632701	Drill Core	0.12	<0.01	0.06	<0.01	2.73	2.62
632702	Drill Core	0.32	<0.01	0.16	<0.01	12.07	2.80
632703	Drill Core	0.40	<0.01	0.20	<0.01	9.58	2.70
632704	Drill Core	0.46	<0.01	0.24	<0.01	5.28	2.60
632705	Drill Core	1.47	<0.01	0.84	<0.01	4.26	2.39
632706	Drill Core	0.46	<0.01	0.24	<0.01	5.58	2.60
632707	Drill Core	0.54	<0.01	0.29	<0.01	8.85	2.63
632708	Drill Core	0.82	<0.01	0.47	<0.01	4.23	2.52
632709	Drill Core	0.34	<0.01	0.17	<0.01	1.64	2.51
632710	Rock Pulp	1.26	0.56	0.28	<0.01	2.17	N.A.



Acme Analytical Laboratories (Vancouver) Ltd.
1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: December 03, 2010

Page: 4 of 5 Part 1

CERTIFICATE OF ANALYSIS

WHI10000655.1

	Method Analyte Unit MDL	7TD.1	WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD
		Pb	Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg
		%	kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%
		0.02	0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01
632711	Drill Core		2.03	0.002	0.005	1.52	4.38	<2	0.007	<0.001	0.03	6.11	<0.02	<0.01	0.011	<0.01	<0.01	9.18	0.11	0.002	0.14
632712	Drill Core		3.27	<0.001	0.002	1.21	2.69	<2	0.003	<0.001	0.03	0.91	<0.02	0.01	0.009	<0.01	<0.01	20.21	0.03	<0.001	0.08
632713	Drill Core		2.75	0.002	0.005	2.30	6.94	3	0.005	<0.001	0.02	2.15	<0.02	<0.01	0.020	<0.01	<0.01	6.67	0.05	<0.001	0.08
632714	Drill Core		3.17	0.001	0.003	0.76	2.96	<2	0.005	<0.001	0.03	1.21	<0.02	0.01	0.008	<0.01	<0.01	14.26	0.08	0.002	0.10
632715	Drill Core		2.78	0.002	0.002	0.76	0.53	<2	0.007	<0.001	0.02	1.60	<0.02	<0.01	0.002	<0.01	<0.01	12.21	0.11	0.003	0.16
632716	Drill Core		4.63	<0.001	0.002	0.45	0.47	<2	0.003	<0.001	0.04	0.84	<0.02	0.02	0.002	<0.01	<0.01	27.44	0.06	0.001	0.09
632717	Drill Core		2.90	0.002	0.002	0.23	0.07	<2	0.006	<0.001	0.02	0.89	<0.02	0.01	<0.001	<0.01	<0.01	18.28	0.11	0.001	0.14
632718	Drill Core		2.90	0.002	0.006	0.41	1.20	<2	0.007	<0.001	0.03	2.84	<0.02	0.01	0.004	<0.01	<0.01	17.14	0.07	0.002	0.15
632719	Drill Core		2.63	0.003	0.006	0.87	5.62	<2	0.008	<0.001	0.03	1.39	<0.02	<0.01	0.018	<0.01	<0.01	10.73	0.09	0.002	0.15
632720	Drill Core		1.36	0.001	0.003	2.30	4.72	<2	0.003	<0.001	0.04	1.03	<0.02	0.01	0.020	<0.01	<0.01	21.14	0.05	0.002	0.11
632721	Drill Core		1.48	0.001	0.003	1.80	4.27	<2	0.004	<0.001	0.04	1.05	<0.02	0.01	0.016	<0.01	<0.01	22.24	0.05	0.002	0.11
632722	Drill Core		2.36	<0.001	0.003	0.24	0.60	<2	0.004	<0.001	0.04	1.19	<0.02	0.01	0.002	<0.01	<0.01	25.60	0.06	0.001	0.10
632723	Drill Core		2.32	0.001	0.005	3.82	6.79	<2	0.003	<0.001	0.04	1.84	<0.02	0.01	0.028	<0.01	<0.01	17.41	0.05	0.001	0.08
632724	Drill Core	10.46	1.49	<0.001	0.004	>10	14.36	3	0.002	<0.001	0.03	1.10	<0.02	<0.01	0.069	<0.01	<0.01	8.31	0.04	0.003	0.06
632725	Drill Core		2.21	<0.001	0.004	9.39	15.08	3	0.002	<0.001	0.03	0.48	<0.02	<0.01	0.066	<0.01	<0.01	15.95	0.04	0.002	0.07
632726	Drill Core	14.02	2.53	<0.001	0.005	>10	19.61	3	<0.001	<0.001	0.02	0.58	<0.02	<0.01	0.099	<0.01	<0.01	14.26	0.02	0.003	0.03
632727	Drill Core	12.72	2.74	<0.001	0.004	>10	14.16	3	0.002	<0.001	0.02	1.36	<0.02	<0.01	0.079	<0.01	<0.01	11.35	0.03	0.003	0.04
632728	Drill Core	11.49	2.36	<0.001	0.004	>10	14.81	2	0.001	<0.001	0.02	1.30	<0.02	<0.01	0.078	<0.01	<0.01	16.47	0.01	0.002	0.03
632729	Drill Core	14.93	2.03	<0.001	0.007	>10	19.29	4	0.001	<0.001	0.02	0.70	<0.02	<0.01	0.100	<0.01	<0.01	14.00	0.03	0.003	0.04
632730	Rock		0.36	<0.001	<0.001	0.12	0.11	<2	<0.001	<0.001	0.02	0.13	<0.02	<0.01	<0.001	<0.01	<0.01	21.75	0.02	<0.001	11.20
632731	Drill Core	14.40	1.98	<0.001	0.006	>10	21.65	5	<0.001	<0.001	0.02	0.51	<0.02	<0.01	0.102	<0.01	<0.01	11.61	0.02	0.003	0.03
632732	Drill Core		1.32	0.002	0.005	6.71	9.48	3	0.004	<0.001	0.03	0.96	<0.02	<0.01	0.043	<0.01	<0.01	12.42	0.04	0.002	0.11
632733	Drill Core		1.27	0.002	0.010	1.82	8.59	2	0.007	<0.001	0.02	1.97	<0.02	<0.01	0.026	<0.01	<0.01	7.09	0.07	0.001	0.10
632734	Drill Core		1.41	0.002	<0.001	0.32	0.25	<2	0.006	<0.001	0.01	0.59	<0.02	<0.01	<0.001	<0.01	<0.01	4.84	0.10	0.002	0.11
632735	Drill Core		1.73	0.002	0.001	0.18	0.71	<2	0.005	<0.001	0.04	0.57	<0.02	<0.01	0.002	<0.01	<0.01	15.36	0.05	0.001	0.11
632736	Drill Core		1.75	0.002	0.008	6.50	14.78	5	0.007	<0.001	0.03	2.80	<0.02	<0.01	0.048	<0.01	<0.01	7.77	0.08	0.003	0.09
632737	Drill Core	12.82	1.64	0.002	0.010	>10	17.75	8	0.007	<0.001	0.02	2.58	<0.02	<0.01	0.057	<0.01	<0.01	4.49	0.08	0.004	0.08
632738	Drill Core		2.26	0.001	0.002	0.06	0.03	<2	0.003	<0.001	0.04	1.09	<0.02	0.02	<0.001	<0.01	<0.01	32.89	0.02	<0.001	0.08
632739	Drill Core		2.25	0.001	0.002	0.03	0.05	<2	0.003	<0.001	0.04	0.50	<0.02	0.02	<0.001	<0.01	<0.01	31.00	0.10	<0.001	0.08
632740	Rock Pulp		0.02	<0.001	0.486	1.42	4.42	25	<0.001	0.001	0.68	5.38	<0.02	0.01	0.028	<0.01	<0.01	4.19	0.04	0.003	1.54



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**

Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: December 03, 2010

Page: 4 of 5 Part 2

CERTIFICATE OF ANALYSIS

WHI10000655.1

	Method Analyte Unit MDL	7TD	7TD	7TD	7TD	7TD	G8SG
		Al	Na	K	W	S	SG
		%	%	%	%	%	
		0.01	0.01	0.01	0.01	0.05	0
632711	Drill Core	1.11	0.02	0.58	<0.01	10.60	2.63
632712	Drill Core	0.38	<0.01	0.20	<0.01	2.78	2.56
632713	Drill Core	0.66	<0.01	0.37	<0.01	6.42	2.58
632714	Drill Core	0.79	<0.01	0.47	<0.01	3.09	2.51
632715	Drill Core	1.27	<0.01	0.72	<0.01	2.22	2.40
632716	Drill Core	0.41	<0.01	0.21	<0.01	1.56	2.54
632717	Drill Core	0.96	<0.01	0.53	<0.01	1.23	2.36
632718	Drill Core	1.13	<0.01	0.66	<0.01	4.26	2.46
632719	Drill Core	1.32	<0.01	0.81	<0.01	4.76	2.41
632720	Drill Core	0.59	<0.01	0.33	<0.01	4.19	2.63
632721	Drill Core	0.72	<0.01	0.42	<0.01	3.86	2.55
632722	Drill Core	0.58	<0.01	0.30	<0.01	1.97	2.43
632723	Drill Core	0.52	<0.01	0.29	<0.01	6.35	2.64
632724	Drill Core	0.37	<0.01	0.21	<0.01	9.71	2.97
632725	Drill Core	0.23	<0.01	0.13	<0.01	9.37	3.05
632726	Drill Core	0.09	<0.01	0.04	<0.01	12.15	3.24
632727	Drill Core	0.19	<0.01	0.10	<0.01	10.31	3.05
632728	Drill Core	0.08	<0.01	0.03	<0.01	10.35	3.05
632729	Drill Core	0.12	<0.01	0.04	<0.01	11.07	3.17
632730	Rock	0.11	0.01	0.01	<0.01	0.28	2.72
632731	Drill Core	0.07	<0.01	0.03	<0.01	12.99	2.82
632732	Drill Core	0.55	<0.01	0.29	<0.01	6.93	2.60
632733	Drill Core	0.77	<0.01	0.45	<0.01	6.62	2.65
632734	Drill Core	0.87	<0.01	0.54	<0.01	0.69	2.38
632735	Drill Core	0.68	<0.01	0.43	<0.01	1.03	2.46
632736	Drill Core	0.71	<0.01	0.39	<0.01	10.99	2.80
632737	Drill Core	0.74	<0.01	0.41	<0.01	12.99	3.05
632738	Drill Core	0.20	<0.01	0.10	<0.01	1.57	2.48
632739	Drill Core	0.21	<0.01	0.11	<0.01	0.86	2.59
632740	Rock Pulp	4.53	0.10	3.35	<0.01	5.12	N.A.



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**

Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: December 03, 2010

Page: 5 of 5 Part 1

CERTIFICATE OF ANALYSIS

WHI10000655.1

	Method Analyte Unit MDL	7TD.1	WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD
		Pb	Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr
		%	kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%
		0.02	0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.01
632741	Drill Core		1.45	<0.001	0.003	0.45	0.11	<2	0.004	<0.001	0.05	1.06	<0.02	0.01	<0.001	<0.01	<0.01	21.65	0.06	0.001
632742	Drill Core		2.16	0.003	0.024	0.39	0.39	<2	0.007	<0.001	0.04	0.76	<0.02	0.02	0.001	<0.01	<0.01	24.43	0.30	0.003
632743	Drill Core		1.94	0.005	0.011	0.12	1.04	2	0.010	<0.001	0.03	0.52	<0.02	0.01	0.003	<0.01	<0.01	20.82	0.40	0.003
632744	Drill Core		1.68	0.004	0.032	0.19	0.26	<2	0.011	<0.001	0.03	0.43	<0.02	0.01	<0.001	<0.01	<0.01	20.97	0.47	0.004
632745	Drill Core		2.21	0.003	0.021	0.11	1.30	<2	0.007	<0.001	0.04	0.74	<0.02	0.02	0.004	<0.01	<0.01	24.27	0.20	0.003
632746	Drill Core		3.31	0.004	0.017	0.15	0.75	2	0.009	<0.001	0.03	0.85	<0.02	0.02	0.002	<0.01	<0.01	23.46	0.40	0.003
632747	Drill Core		2.39	0.003	0.006	0.03	0.30	<2	0.006	<0.001	0.02	0.99	<0.02	<0.01	<0.001	<0.01	<0.01	12.65	0.29	0.002
632748	Drill Core		2.84	0.002	0.015	0.07	0.62	<2	0.007	<0.001	0.01	2.63	<0.02	<0.01	0.002	<0.01	<0.01	8.93	0.12	0.002
632749	Drill Core		0.70	0.008	0.010	0.26	3.06	6	0.018	<0.001	0.02	3.15	<0.02	<0.01	0.008	<0.01	<0.01	4.27	0.34	0.005
632750	Drill Core		2.88	0.012	0.021	0.08	0.55	3	0.020	<0.001	<0.01	2.16	<0.02	<0.01	0.002	<0.01	<0.01	2.55	0.26	0.004
632751	Drill Core		0.53	0.009	0.008	0.29	2.69	6	0.016	<0.001	0.01	1.91	<0.02	<0.01	0.007	<0.01	<0.01	2.87	0.27	0.005
632752	Drill Core		1.62	0.005	0.012	0.54	0.27	4	0.022	<0.001	<0.01	1.90	<0.02	<0.01	<0.001	<0.01	<0.01	7.48	2.06	0.011
632753	Drill Core		2.78	<0.001	0.004	<0.02	<0.01	<2	0.005	<0.001	0.02	3.17	<0.02	0.01	<0.001	<0.01	<0.01	12.48	0.05	0.005
632754	Drill Core		3.11	<0.001	0.002	<0.02	<0.01	<2	0.002	<0.001	0.04	1.60	<0.02	0.02	<0.001	<0.01	<0.01	26.07	0.02	0.002



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: December 03, 2010

Page: 5 of 5 **Part** 2

CERTIFICATE OF ANALYSIS

WHI10000655.1

	Method	7TD	7TD	7TD	7TD	7TD	G8SG
	Analyte	Al	Na	K	W	S	SG
	Unit	%	%	%	%	%	
	MDL	0.01	0.01	0.01	0.01	0.05	0
632741	Drill Core	0.32	<0.01	0.18	<0.01	1.49	2.54
632742	Drill Core	0.59	<0.01	0.31	<0.01	1.30	2.47
632743	Drill Core	0.71	<0.01	0.40	<0.01	1.27	2.35
632744	Drill Core	0.76	<0.01	0.43	<0.01	0.75	2.39
632745	Drill Core	0.54	<0.01	0.30	<0.01	1.71	2.48
632746	Drill Core	0.66	<0.01	0.37	<0.01	1.54	2.38
632747	Drill Core	0.42	<0.01	0.23	<0.01	1.32	2.46
632748	Drill Core	0.46	<0.01	0.27	<0.01	3.44	2.49
632749	Drill Core	1.27	<0.01	0.78	<0.01	5.18	2.34
632750	Drill Core	1.64	<0.01	0.92	<0.01	2.75	2.22
632751	Drill Core	1.39	<0.01	0.81	<0.01	3.40	2.26
632752	Drill Core	2.10	<0.01	1.36	<0.01	2.39	2.16
632753	Drill Core	3.38	<0.01	2.39	<0.01	3.66	2.59
632754	Drill Core	2.15	<0.01	1.22	<0.01	1.84	2.60



Acme Analytical Laboratories (Vancouver) Ltd.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: **Selwyn Resources Ltd.**

Suite 700 - 509 Richards Street

Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: December 03, 2010

Page: 1 of 2 Part 1

QUALITY CONTROL REPORT

WHI10000655.1

	Method Analyte Unit MDL	7TD.1	WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD
		Pb	Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg
		%	kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%
		0.02	0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01
Pulp Duplicates																					
632667	Drill Core		1.63	0.002	0.001	0.02	0.72	<2	0.006	<0.001	<0.01	0.66	<0.02	<0.01	0.002	<0.01	<0.01	2.92	0.04	0.002	0.06
REP 632667	QC			0.002	0.001	0.02	0.72	<2	0.006	<0.001	<0.01	0.69	<0.02	<0.01	0.003	<0.01	<0.01	2.98	0.04	0.001	0.06
632688	Drill Core	18.41	0.52	<0.001	0.005	>10	3.83	4	0.003	<0.001	0.03	2.62	<0.02	<0.01	0.011	<0.01	<0.01	6.82	0.02	<0.001	0.04
REP 632688	QC	18.18																			
REP 632704	QC			<0.001	0.002	2.17	4.61	<2	0.003	<0.001	0.04	1.78	<0.02	0.01	0.015	<0.01	<0.01	21.67	0.06	<0.001	0.11
632723	Drill Core		2.32	0.001	0.005	3.82	6.79	<2	0.003	<0.001	0.04	1.84	<0.02	0.01	0.028	<0.01	<0.01	17.41	0.05	0.001	0.08
REP 632723	QC			0.001	0.005	3.92	6.95	<2	0.004	<0.001	0.04	1.89	<0.02	0.01	0.029	<0.01	<0.01	17.81	0.05	0.002	0.08
632737	Drill Core	12.82	1.64	0.002	0.010	>10	17.75	8	0.007	<0.001	0.02	2.58	<0.02	<0.01	0.057	<0.01	<0.01	4.49	0.08	0.004	0.08
REP 632737	QC	12.94																			
Core Reject Duplicates																					
632669	Drill Core		0.70	0.003	0.002	<0.02	1.48	<2	0.010	<0.001	<0.01	0.82	<0.02	<0.01	0.005	<0.01	<0.01	0.31	0.03	0.001	0.12
DUP 632669	QC			0.003	0.002	<0.02	1.48	<2	0.010	<0.001	<0.01	0.85	<0.02	<0.01	0.005	<0.01	<0.01	0.33	0.04	0.001	0.12
632704	Drill Core		2.01	<0.001	0.002	2.19	4.67	<2	0.003	<0.001	0.04	1.82	<0.02	0.01	0.016	<0.01	<0.01	21.97	0.06	0.001	0.11
DUP 632704	QC			<0.001	0.002	2.19	4.67	<2	0.003	<0.001	0.04	1.78	<0.02	0.01	0.015	<0.01	<0.01	21.31	0.06	0.001	0.11
632739	Drill Core		2.25	0.001	0.002	0.03	0.05	<2	0.003	<0.001	0.04	0.50	<0.02	0.02	<0.001	<0.01	<0.01	31.00	0.10	<0.001	0.08
DUP 632739	QC			0.001	0.002	0.02	0.04	<2	0.003	<0.001	0.04	0.50	<0.02	0.02	<0.001	<0.01	<0.01	30.82	0.09	<0.001	0.08
Reference Materials																					
STD CCU-1C	Standard	0.40																			
STD CCU-1C	Standard	0.40																			
STD CCU-1C	Standard	0.39																			
STD CZN-3	Standard	0.10																			
STD CZN-3	Standard	0.09																			
STD CZN-3	Standard	0.12																			
STD OREAS131A	Standard			<0.001	0.032	1.72	2.94	31	0.002	0.002	0.17	5.90	<0.02	<0.01	0.008	<0.01	<0.01	5.46	0.06	0.002	3.13
STD OREAS131A	Standard			<0.001	0.032	1.69	2.85	31	0.003	0.002	0.16	5.82	<0.02	<0.01	0.008	<0.01	<0.01	5.37	0.05	0.002	3.05
STD OREAS131A	Standard			<0.001	0.032	1.72	2.90	32	0.003	0.002	0.17	5.77	<0.02	<0.01	0.008	<0.01	<0.01	5.35	0.06	0.002	3.17
STD OREAS131A	Standard			<0.001	0.033	1.69	2.92	32	0.003	0.002	0.19	6.00	<0.02	<0.01	0.009	<0.01	<0.01	5.54	0.06	0.003	3.20
STD PTC-1A	Standard	0.06																			



Acme Analytical Laboratories (Vancouver) Ltd.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: Selwyn Resources Ltd.

Suite 700 - 509 Richards Street

Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: December 03, 2010

Page: 1 of 2 **Part** 2

QUALITY CONTROL REPORT

WHI10000655.1

Method		7TD	7TD	7TD	7TD	7TD	G8SG
Analyte		Al	Na	K	W	S	SG
Unit		%	%	%	%	%	
MDL		0.01	0.01	0.01	0.01	0.05	0
Pulp Duplicates							
632667	Drill Core	0.53	<0.01	0.28	<0.01	0.87	2.38
REP 632667	QC	0.54	<0.01	0.28	<0.01	0.89	
632688	Drill Core	0.22	<0.01	0.11	<0.01	7.91	2.95
REP 632688	QC						
REP 632704	QC	0.45	<0.01	0.23	<0.01	5.20	
632723	Drill Core	0.52	<0.01	0.29	<0.01	6.35	2.64
REP 632723	QC	0.53	<0.01	0.30	<0.01	6.52	
632737	Drill Core	0.74	<0.01	0.41	<0.01	12.99	3.05
REP 632737	QC						
Core Reject Duplicates							
632669	Drill Core	0.99	<0.01	0.58	<0.01	1.48	2.27
DUP 632669	QC	1.03	<0.01	0.59	<0.01	1.50	2.24
632704	Drill Core	0.46	<0.01	0.24	<0.01	5.28	2.60
DUP 632704	QC	0.46	<0.01	0.24	<0.01	5.18	2.59
632739	Drill Core	0.21	<0.01	0.11	<0.01	0.86	2.59
DUP 632739	QC	0.21	<0.01	0.11	<0.01	0.85	2.51
Reference Materials							
STD CCU-1C	Standard						
STD CCU-1C	Standard						
STD CCU-1C	Standard						
STD CZN-3	Standard						
STD CZN-3	Standard						
STD CZN-3	Standard						
STD OREAS131A	Standard	4.64	0.16	3.51	<0.01	5.18	
STD OREAS131A	Standard	4.46	0.15	3.39	<0.01	4.87	
STD OREAS131A	Standard	4.70	0.15	3.39	<0.01	4.83	
STD OREAS131A	Standard	4.67	0.16	3.65	<0.01	5.11	
STD PTC-1A	Standard						



Acme Analytical Laboratories (Vancouver) Ltd.
1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: December 03, 2010

Page: 2 of 2 Part 1

QUALITY CONTROL REPORT

WHI10000655.1

		7TD.1 Pb % 0.02	WGHT Wgt kg 0.01	7TD Mo % 0.001	7TD Cu % 0.001	7TD Pb % 0.02	7TD Zn % 0.01	7TD Ag gm/t 2	7TD Ni % 0.001	7TD Co % 0.001	7TD Mn % 0.01	7TD Fe % 0.01	7TD As % 0.02	7TD Sr % 0.01	7TD Cd % 0.001	7TD Sb % 0.01	7TD Bi % 0.01	7TD Ca % 0.01	7TD P % 0.01	7TD Cr % 0.001	7TD Mg % 0.01
STD PTC-1A	Standard	0.05																			
STD PTC-1A	Standard	0.05																			
STD R4T	Standard			0.063	0.516	1.53	3.49	87	0.353	0.041	0.09	24.72	<0.02	0.02	0.019	0.01	<0.01	2.20	0.05	0.019	1.41
STD R4T	Standard			0.065	0.525	1.64	3.54	90	0.360	0.044	0.09	24.88	<0.02	0.02	0.019	0.01	<0.01	2.24	0.05	0.019	1.45
STD R4T	Standard			0.060	0.505	1.50	3.46	87	0.354	0.039	0.09	24.15	<0.02	0.02	0.018	0.01	<0.01	2.21	0.05	0.018	1.44
STD R4T	Standard			0.066	0.530	1.59	3.57	91	0.360	0.044	0.10	25.23	<0.02	0.02	0.020	0.01	<0.01	2.31	0.05	0.018	1.47
STD SARM 71	Standard	<0.02																			
STD SARM 71	Standard	<0.02																			
STD SARM 71	Standard	<0.02																			
STD SU-1B	Standard			<0.001	1.192	<0.02	0.03	9	1.999	0.067	0.07	25.89	<0.02	0.03	<0.001	<0.01	<0.01	2.23	0.08	0.031	1.78
STD SU-1B	Standard			<0.001	1.187	<0.02	0.05	7	2.003	0.069	0.07	25.98	<0.02	0.03	<0.001	<0.01	<0.01	2.26	0.06	0.032	1.82
STD SU-1B	Standard			<0.001	1.179	<0.02	0.03	6	1.989	0.065	0.07	25.19	<0.02	0.03	<0.001	<0.01	<0.01	2.24	0.06	0.031	1.81
STD SU-1B	Standard			<0.001	1.204	<0.02	0.03	7	1.969	0.068	0.07	26.14	<0.02	0.03	<0.001	<0.01	0.01	2.29	0.07	0.030	1.82
STD R4T Expected				0.062	0.502	1.518	3.376	86	0.339	0.039	0.086	24.07	0.0087	0.0185	0.018	0.0138	0.0018	2.166	0.045	0.018	1.384
STD OREAS131A Expected				0.001	0.0322	1.72	2.83	30.9	0.0027	0.0023	0.1722	5.8166	0.0082	0.0028	0.0081	0.0047	0.001	5.286	0.0536	0.0025	3.1182
STD SU-1B Expected				0.0004	1.185	0.0058	0.0235	6.4	1.97	0.0672	0.0703	25.54	0.00025	0.03	0.0003	0.00002	0.0003	2.21	0.06	0.032	1.79
STD CZN-3 Expected		0.113																			
STD CCU-1C Expected		0.34																			
STD PTC-1A Expected		0.05																			
BLK	Blank			<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	<0.01	<0.01	<0.02	<0.01	<0.001	<0.01	<0.01	<0.01	<0.01	<0.001	<0.01
BLK	Blank			<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	<0.01	<0.01	<0.02	<0.01	<0.001	<0.01	<0.01	<0.01	<0.01	<0.001	<0.01
BLK	Blank			<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	<0.01	<0.01	<0.02	<0.01	<0.001	<0.01	<0.01	<0.01	<0.01	<0.001	<0.01
BLK	Blank			<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	<0.01	<0.01	<0.02	<0.01	<0.001	<0.01	<0.01	<0.01	<0.01	<0.001	<0.01
BLK	Blank	<0.02																			
BLK	Blank	<0.02																			
BLK	Blank	<0.02																			
Prep Wash																					
G1	Prep Blank			<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	0.07	2.25	<0.02	0.07	<0.001	<0.01	<0.01	2.25	0.08	<0.001	0.55
G1	Prep Blank			<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	0.08	2.31	<0.02	0.07	<0.001	<0.01	<0.01	2.30	0.08	<0.001	0.59



Acme Analytical Laboratories (Vancouver) Ltd.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: **Selwyn Resources Ltd.**

Suite 700 - 509 Richards Street

Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: December 03, 2010

Page: 2 of 2 **Part** 2

QUALITY CONTROL REPORT

WHI10000655.1

		7TD Al %	7TD Na %	7TD K %	7TD W %	7TD S %	G8SG SG
		0.01	0.01	0.01	0.01	0.05	0
STD PTC-1A	Standard						
STD PTC-1A	Standard						
STD R4T	Standard	3.94	0.94	1.19	<0.01	13.28	
STD R4T	Standard	3.96	0.95	1.21	<0.01	12.23	
STD R4T	Standard	3.98	0.93	1.18	<0.01	12.60	
STD R4T	Standard	4.04	0.98	1.24	<0.01	12.89	
STD SARM 71	Standard						
STD SARM 71	Standard						
STD SARM 71	Standard						
STD SU-1B	Standard	4.35	1.75	0.63	<0.01	11.35	
STD SU-1B	Standard	4.35	1.70	0.64	<0.01	8.91	
STD SU-1B	Standard	4.44	1.70	0.60	<0.01	8.80	
STD SU-1B	Standard	4.43	1.79	0.65	<0.01	9.81	
STD R4T Expected		3.897	0.9	1.153	0.00016	12.9903	
STD OREAS131A Expected		4.6057	0.1501	3.1584	0.0005	4.8	
STD SU-1B Expected		4.39	1.662	0.6	0.0007	8.76	
STD CZN-3 Expected							
STD CCU-1C Expected							
STD PTC-1A Expected							
BLK	Blank	<0.01	<0.01	<0.01	<0.01	<0.05	
BLK	Blank	<0.01	<0.01	<0.01	<0.01	<0.05	
BLK	Blank	<0.01	<0.01	<0.01	<0.01	<0.05	
BLK	Blank	<0.01	<0.01	<0.01	<0.01	<0.05	
BLK	Blank						
BLK	Blank						
BLK	Blank						
Prep Wash							
G1	Prep Blank	5.92	2.70	2.96	<0.01	0.11	2.64
G1	Prep Blank	6.31	2.75	3.11	<0.01	<0.05	2.69



1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: Selwyn Resources Ltd.

Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Submitted By: Jason K. Dunning

Receiving Lab: Canada-Whitehorse

Received: November 15, 2010

Report Date: December 01, 2010

Page: 1 of 2

CERTIFICATE OF ANALYSIS

WHI10000654.1

CLIENT JOB INFORMATION

Project: Selwyn Project
Shipment ID:
P.O. Number 1040
Number of Samples: 30

SAMPLE DISPOSAL

STOR-PLP Store After 90 days Invoice for Storage
STOR-RJT Store After 90 days Invoice for Storage

Acme does not accept responsibility for samples left at the laboratory after 90 days without prior written instructions for sample storage or return.

Invoice To: Selwyn Resources Ltd.
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6
Canada

CC:

SAMPLE PREPARATION AND ANALYTICAL PROCEDURES

Method Code	Number of Samples	Code Description	Test Wgt (g)	Report Status	Lab
R200-250	30	Crush split and pulverize 250g drill core to 200 mesh			WHI
7TD2	30	4 Acid digestion ICP-ES analysis.	0.5	Completed	VAN
G812	30	Specific Gravity on Pulp		Completed	VAN

ADDITIONAL COMMENTS



This report supersedes all previous preliminary and final reports with this file number dated prior to the date on this certificate. Signature indicates final approval; preliminary reports are unsigned and should be used for reference only.
All results are considered the confidential property of the client. Acme assumes the liabilities for actual cost of analysis only.
** asterisk indicates that an analytical result could not be provided due to unusually high levels of interference from other elements.



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: December 01, 2010

Page: 2 of 2 Part 1

CERTIFICATE OF ANALYSIS

WHI10000654.1

	Method Analyte Unit MDL	WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD
		Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg	Al
		kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%	%
		0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01	0.01
631401	Drill Core	1.11	0.001	0.007	0.09	0.15	<2	0.013	<0.001	<0.01	1.86	<0.02	<0.01	<0.001	<0.01	<0.01	7.81	2.09	0.009	0.65	3.40
631402	Drill Core	0.87	0.002	0.009	0.17	3.04	4	0.010	<0.001	0.02	3.36	<0.02	0.01	0.009	<0.01	<0.01	10.55	1.19	0.005	0.51	2.43
631403	Drill Core	0.58	0.002	0.008	0.21	1.81	3	0.010	<0.001	0.02	3.55	<0.02	0.01	0.005	<0.01	<0.01	11.50	1.47	0.006	0.44	2.26
631404	Drill Core	0.48	0.001	0.009	0.31	4.92	5	0.007	<0.001	0.02	3.49	<0.02	0.01	0.015	<0.01	<0.01	15.06	0.65	0.005	0.36	1.84
631405	Drill Core	2.55	0.002	0.007	<0.02	<0.01	<2	0.010	<0.001	0.02	1.63	<0.02	0.01	<0.001	<0.01	<0.01	12.35	1.20	0.007	0.64	3.30
631406	Drill Core	1.11	0.002	0.009	2.16	6.49	3	0.006	<0.001	0.01	3.73	<0.02	<0.01	0.034	<0.01	<0.01	1.27	0.02	0.002	0.07	0.69
631407	Drill Core	0.94	0.002	0.005	1.02	5.70	<2	0.005	<0.001	0.03	3.51	<0.02	<0.01	0.023	<0.01	<0.01	11.05	0.03	0.001	0.08	0.58
631408	Drill Core	1.08	0.003	0.008	1.77	9.83	2	0.007	<0.001	0.01	3.94	<0.02	<0.01	0.039	<0.01	<0.01	1.45	0.04	0.003	0.08	0.81
631409	Drill Core	0.91	0.002	0.006	1.95	7.92	<2	0.004	<0.001	<0.01	2.95	<0.02	<0.01	0.030	<0.01	<0.01	0.62	0.02	0.001	0.05	0.50
631410	Drill Core	0.49	0.003	0.011	1.78	8.77	3	0.007	<0.001	0.01	8.42	<0.02	<0.01	0.031	<0.01	<0.01	0.14	0.03	0.002	0.06	0.65
631411	Drill Core	0.43	0.002	0.009	1.52	8.17	3	0.006	<0.001	0.01	6.92	<0.02	<0.01	0.029	<0.01	<0.01	0.13	0.02	0.002	0.06	0.60
631412	Drill Core	1.18	0.002	0.006	0.16	0.07	<2	0.010	<0.001	0.01	11.84	<0.02	<0.01	<0.001	<0.01	<0.01	1.31	0.03	0.002	0.07	0.66
631413	Drill Core	0.82	0.002	0.004	0.13	1.56	<2	0.008	<0.001	0.02	2.54	<0.02	<0.01	0.004	<0.01	<0.01	6.85	0.03	0.002	0.08	0.73
631414	Drill Core	0.95	0.004	0.008	1.48	10.17	3	0.008	<0.001	0.01	3.64	<0.02	<0.01	0.027	<0.01	<0.01	2.14	0.07	0.002	0.09	0.91
631415	Drill Core	0.63	<0.001	<0.001	0.64	0.16	<2	<0.001	<0.001	0.09	1.09	<0.02	0.01	<0.001	<0.01	<0.01	31.87	0.02	<0.001	0.09	0.07
631416	Drill Core	0.62	0.002	0.002	0.37	1.68	<2	0.005	<0.001	0.02	0.96	<0.02	<0.01	0.004	<0.01	<0.01	13.13	0.05	<0.001	0.08	0.59
631417	Drill Core	1.53	0.001	0.002	0.50	2.66	<2	0.002	<0.001	0.02	0.41	<0.02	<0.01	0.008	<0.01	<0.01	14.74	0.02	<0.001	0.04	0.24
631418	Drill Core	0.55	<0.001	<0.001	0.27	0.67	<2	0.001	<0.001	0.08	0.48	<0.02	0.02	0.002	<0.01	<0.01	32.17	0.03	<0.001	0.10	0.14
631419	Drill Core	0.97	0.001	0.002	0.05	0.43	<2	0.004	<0.001	<0.01	1.08	<0.02	<0.01	0.001	<0.01	<0.01	2.61	0.02	<0.001	0.04	0.35
631420	Rock	0.43	<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	0.01	0.10	<0.02	<0.01	<0.001	<0.01	<0.01	20.49	0.02	<0.001	10.56	0.12
631421	Drill Core	0.96	0.001	0.003	1.68	5.14	<2	0.004	<0.001	0.01	2.40	<0.02	<0.01	0.012	<0.01	<0.01	3.21	0.03	0.001	0.05	0.46
631422	Drill Core	1.10	0.002	0.006	4.71	16.65	5	0.005	<0.001	0.04	4.07	<0.02	<0.01	0.042	<0.01	<0.01	14.77	0.03	0.002	0.06	0.35
631423	Drill Core	1.32	0.001	0.003	1.31	3.69	<2	0.005	<0.001	0.03	1.78	<0.02	<0.01	0.010	<0.01	<0.01	12.28	0.07	0.002	0.10	0.68
631424	Drill Core	0.58	0.001	0.007	1.07	8.12	<2	0.006	<0.001	0.02	1.45	<0.02	<0.01	0.023	<0.01	<0.01	8.39	0.05	0.002	0.10	0.83
631425	Drill Core	1.32	0.002	0.001	1.78	1.67	<2	0.003	<0.001	0.03	0.85	<0.02	0.01	0.007	<0.01	<0.01	20.26	0.08	0.003	0.12	0.80
631426	Drill Core	2.36	0.001	0.002	0.11	0.13	<2	0.004	<0.001	0.03	0.89	<0.02	0.01	<0.001	<0.01	<0.01	24.26	0.05	<0.001	0.10	0.55
631427	Drill Core	0.46	0.002	0.004	<0.02	<0.01	<2	0.008	<0.001	0.01	1.33	<0.02	<0.01	<0.001	<0.01	<0.01	7.44	0.03	0.001	0.09	0.60
631428	Drill Core	0.84	0.001	0.004	0.34	0.01	<2	0.010	<0.001	0.04	2.44	<0.02	0.01	<0.001	<0.01	<0.01	21.96	0.06	0.002	0.11	0.64
631429	Drill Core	2.46	0.001	0.003	<0.02	<0.01	<2	0.004	<0.001	0.03	0.49	<0.02	0.01	<0.001	<0.01	<0.01	23.62	0.15	0.002	0.09	0.46
631430	Rock Pulp	0.08	0.002	0.794	0.87	1.30	211	0.002	0.002	0.22	2.61	<0.02	0.01	0.009	0.04	<0.01	1.89	0.01	0.003	0.12	1.22



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: December 01, 2010

Page: 2 of 2 **Part** 2

CERTIFICATE OF ANALYSIS

WHI10000654.1

	Method	7TD	7TD	7TD	7TD	G8SG
	Analyte	Na	K	W	S	SG
	Unit	%	%	%	%	
	MDL	0.01	0.01	0.01	0.05	0
631401	Drill Core	0.01	2.09	<0.01	2.05	2.15
631402	Drill Core	<0.01	1.42	<0.01	5.34	2.47
631403	Drill Core	<0.01	1.33	<0.01	4.96	2.35
631404	Drill Core	<0.01	1.05	<0.01	6.53	2.46
631405	Drill Core	<0.01	1.94	<0.01	1.79	2.27
631406	Drill Core	<0.01	0.40	<0.01	7.49	2.66
631407	Drill Core	<0.01	0.33	<0.01	6.98	2.61
631408	Drill Core	<0.01	0.47	<0.01	9.14	2.66
631409	Drill Core	<0.01	0.28	<0.01	7.12	2.65
631410	Drill Core	<0.01	0.38	<0.01	13.58	2.73
631411	Drill Core	<0.01	0.35	<0.01	11.61	2.80
631412	Drill Core	<0.01	0.38	<0.01	13.36	2.68
631413	Drill Core	<0.01	0.43	<0.01	3.65	2.43
631414	Drill Core	<0.01	0.56	<0.01	9.01	2.58
631415	Drill Core	<0.01	0.03	<0.01	1.72	2.57
631416	Drill Core	<0.01	0.33	<0.01	2.03	2.42
631417	Drill Core	<0.01	0.12	<0.01	1.89	2.53
631418	Drill Core	<0.01	0.07	<0.01	1.18	2.57
631419	Drill Core	<0.01	0.19	<0.01	1.35	2.48
631420	Rock	<0.01	0.02	<0.01	0.18	2.64
631421	Drill Core	<0.01	0.25	<0.01	5.31	2.64
631422	Drill Core	<0.01	0.19	<0.01	13.38	2.94
631423	Drill Core	<0.01	0.40	<0.01	4.11	2.55
631424	Drill Core	<0.01	0.52	<0.01	5.77	2.58
631425	Drill Core	<0.01	0.47	<0.01	2.22	2.48
631426	Drill Core	<0.01	0.31	<0.01	1.24	2.49
631427	Drill Core	<0.01	0.35	<0.01	1.45	2.45
631428	Drill Core	<0.01	0.40	<0.01	3.05	2.52
631429	Drill Core	<0.01	0.25	<0.01	0.71	2.43
631430	Rock Pulp	0.56	0.27	<0.01	2.02	N.A.



Acme Analytical Laboratories (Vancouver) Ltd.
1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: December 01, 2010

Page: 1 of 1 Part 1

QUALITY CONTROL REPORT

WHI10000654.1

	Method Analyte Unit MDL	WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD
		Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg	Al
		kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%	%
		0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01	0.01
Pulp Duplicates																					
631416	Drill Core	0.62	0.002	0.002	0.37	1.68	<2	0.005	<0.001	0.02	0.96	<0.02	<0.01	0.004	<0.01	<0.01	13.13	0.05	<0.001	0.08	0.59
REP 631416	QC		0.002	0.002	0.37	1.66	<2	0.005	<0.001	0.02	0.95	<0.02	<0.01	0.004	<0.01	<0.01	12.98	0.05	0.001	0.07	0.59
Core Reject Duplicates																					
631407	Drill Core	0.94	0.002	0.005	1.02	5.70	<2	0.005	<0.001	0.03	3.51	<0.02	<0.01	0.023	<0.01	<0.01	11.05	0.03	0.001	0.08	0.58
DUP 631407	QC		0.002	0.006	1.06	5.91	2	0.005	<0.001	0.03	3.68	<0.02	<0.01	0.024	<0.01	<0.01	10.83	0.03	0.001	0.08	0.60
Reference Materials																					
STD OREAS131A	Standard		0.001	0.032	1.63	2.84	31	0.002	0.002	0.17	5.81	<0.02	<0.01	0.008	<0.01	<0.01	5.32	0.05	0.003	3.05	4.50
STD R4T	Standard		0.062	0.504	1.47	3.39	86	0.346	0.040	0.09	24.13	<0.02	0.02	0.019	0.02	<0.01	2.18	0.04	0.013	1.38	3.84
STD SU-1B	Standard		<0.001	1.183	<0.02	0.03	7	1.977	0.068	0.07	25.76	<0.02	0.03	<0.001	<0.01	<0.01	2.29	0.07	0.030	1.80	4.35
STD R4T Expected			0.062	0.502	1.518	3.376	86	0.339	0.039	0.086	24.07	0.0087	0.0185	0.018	0.0138	0.0018	2.166	0.045	0.018	1.384	3.897
STD OREAS131A Expected			0.001	0.0322	1.72	2.83	30.9	0.0027	0.0023	0.1722	5.8166	0.0082	0.0028	0.0081	0.0047	0.001	5.286	0.0536	0.0025	3.1182	4.6057
STD SU-1B Expected			0.0004	1.185	0.0058	0.0235	6.4	1.97	0.0672	0.0703	25.54	0.00025	0.03	0.0003	0.00002	0.0003	2.21	0.06	0.032	1.79	4.39
BLK	Blank		<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	<0.01	<0.01	<0.02	<0.01	<0.001	<0.01	<0.01	<0.01	<0.01	<0.001	<0.01	<0.01
Prep Wash																					
G1	Prep Blank		<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	0.08	2.54	<0.02	0.07	<0.001	<0.01	<0.01	2.43	0.09	<0.001	0.69	7.83
G1	Prep Blank		<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	0.07	2.43	<0.02	0.07	<0.001	<0.01	<0.01	2.43	0.08	<0.001	0.64	7.67



Acme Analytical Laboratories (Vancouver) Ltd.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: **Selwyn Resources Ltd.**

Suite 700 - 509 Richards Street

Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: December 01, 2010

Page: 1 of 1 **Part** 2

QUALITY CONTROL REPORT

WHI10000654.1

		Method	7TD	7TD	7TD	7TD	G8SG
		Analyte	Na	K	W	S	SG
		Unit	%	%	%	%	
		MDL	0.01	0.01	0.01	0.05	0
Pulp Duplicates							
631416	Drill Core		<0.01	0.33	<0.01	2.03	2.42
REP 631416	QC		<0.01	0.33	<0.01	2.01	
Core Reject Duplicates							
631407	Drill Core		<0.01	0.33	<0.01	6.98	2.61
DUP 631407	QC		<0.01	0.33	<0.01	7.21	2.63
Reference Materials							
STD OREAS131A	Standard		0.15	3.41	<0.01	4.74	
STD R4T	Standard		0.92	1.17	<0.01	14.85	
STD SU-1B	Standard		1.72	0.64	<0.01	11.88	
STD R4T Expected			0.9	1.153	0.00016	12.9903	
STD OREAS131A Expected			0.1501	3.1584	0.0005	4.8	
STD SU-1B Expected			1.662	0.6	0.0007	8.76	
BLK	Blank		<0.01	<0.01	<0.01	<0.05	
Prep Wash							
G1	Prep Blank		2.69	3.16	<0.01	<0.05	2.73
G1	Prep Blank		2.68	3.09	<0.01	<0.05	2.72



1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**

Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Submitted By: Jason K. Dunning

Receiving Lab: Canada-Whitehorse

Received: November 15, 2010

Report Date: December 16, 2010

Page: 1 of 3

CERTIFICATE OF ANALYSIS

WHI10000653.1

CLIENT JOB INFORMATION

Project: Selwyn Project
Shipment ID:
P.O. Number 1038
Number of Samples: 34

SAMPLE DISPOSAL

STOR-PLP Store After 90 days Invoice for Storage
STOR-RJT Store After 90 days Invoice for Storage

Acme does not accept responsibility for samples left at the laboratory after 90 days without prior written instructions for sample storage or return.

Invoice To: Selwyn Resources Ltd.
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6
Canada

CC:

SAMPLE PREPARATION AND ANALYTICAL PROCEDURES

Method Code	Number of Samples	Code Description	Test Wgt (g)	Report Status	Lab
R200-250	34	Crush split and pulverize 250g drill core to 200 mesh			WHI
7TD2	34	4 Acid digestion ICP-ES analysis.	0.5	Completed	VAN
G812	34	Specific Gravity on Pulp		Completed	VAN

ADDITIONAL COMMENTS



This report supersedes all previous preliminary and final reports with this file number dated prior to the date on this certificate. Signature indicates final approval; preliminary reports are unsigned and should be used for reference only.
All results are considered the confidential property of the client. Acme assumes the liabilities for actual cost of analysis only.
** asterisk indicates that an analytical result could not be provided due to unusually high levels of interference from other elements.



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: December 16, 2010

Page: 2 of 3 Part 1

CERTIFICATE OF ANALYSIS

WHI10000653.1

	Method Analyte Unit MDL	WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD
		Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg	Al
		kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%	%
		0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01	0.01
633101	Drill Core	2.95	0.002	0.007	0.34	0.24	<2	0.010	<0.001	<0.01	1.61	<0.02	<0.01	<0.001	<0.01	<0.01	3.53	0.98	0.004	0.16	1.66
633102	Drill Core	1.46	<0.001	0.002	<0.02	0.25	<2	0.003	<0.001	0.06	0.63	<0.02	0.01	<0.001	<0.01	<0.01	22.03	0.17	<0.001	0.11	0.42
633103	Drill Core	0.85	<0.001	0.002	0.13	0.44	<2	0.005	<0.001	0.04	0.69	<0.02	0.02	0.002	<0.01	<0.01	18.21	0.41	0.002	0.17	0.90
633104	Drill Core	1.33	<0.001	0.002	1.34	4.25	<2	0.003	<0.001	0.03	1.16	<0.02	0.01	0.013	<0.01	<0.01	11.47	0.05	<0.001	0.09	0.38
633105	Drill Core	2.05	0.001	0.004	1.66	5.15	<2	0.004	<0.001	0.03	3.27	<0.02	0.01	0.013	<0.01	<0.01	14.38	0.05	<0.001	0.09	0.58
633106	Drill Core	2.11	0.001	0.002	0.73	2.14	<2	0.003	<0.001	0.04	1.06	<0.02	0.01	0.005	<0.01	<0.01	20.55	0.05	<0.001	0.10	0.53
633107	Drill Core	3.51	0.002	0.004	1.84	5.81	<2	0.005	<0.001	0.02	1.70	<0.02	<0.01	0.015	<0.01	<0.01	7.82	0.06	<0.001	0.08	0.66
633108	Drill Core	1.11	<0.001	0.003	2.02	7.31	<2	0.002	<0.001	0.02	1.14	<0.02	<0.01	0.029	<0.01	<0.01	15.95	0.03	<0.001	0.05	0.22
633109	Drill Core	1.97	0.001	0.002	1.17	1.91	<2	0.004	<0.001	0.03	0.77	<0.02	0.01	0.006	<0.01	<0.01	19.16	0.04	0.001	0.10	0.69
633110	Drill Core	0.66	0.001	0.002	3.16	0.91	<2	0.003	<0.001	0.03	0.56	<0.02	<0.01	0.003	<0.01	<0.01	14.57	0.05	0.002	0.08	0.50
633111	Drill Core	0.67	<0.001	0.002	3.61	0.41	<2	0.003	<0.001	0.02	0.61	<0.02	<0.01	0.001	<0.01	<0.01	14.99	0.05	0.002	0.09	0.58
633112	Drill Core	1.37	0.001	0.001	0.06	0.12	<2	0.004	<0.001	0.02	0.49	<0.02	<0.01	<0.001	<0.01	<0.01	13.89	0.06	0.002	0.09	0.66
633113	Drill Core	1.99	<0.001	0.001	0.05	0.27	<2	0.003	<0.001	0.03	0.49	<0.02	0.02	<0.001	<0.01	<0.01	25.79	0.04	<0.001	0.09	0.48
633114	Drill Core	2.60	0.001	0.003	0.20	0.07	<2	0.004	<0.001	0.04	1.04	<0.02	0.02	<0.001	<0.01	<0.01	25.22	0.05	0.002	0.11	0.71
633115	Drill Core	1.76	0.002	0.003	0.06	0.46	<2	0.005	<0.001	0.03	0.52	<0.02	0.01	0.001	<0.01	<0.01	14.61	0.06	<0.001	0.11	0.83
633116	Drill Core	1.56	<0.001	0.002	<0.02	0.08	<2	0.003	<0.001	0.02	0.24	<0.02	0.01	<0.001	<0.01	<0.01	18.71	0.03	<0.001	0.06	0.32
633117	Drill Core	2.57	<0.001	0.003	0.10	0.07	<2	0.004	<0.001	0.02	1.36	<0.02	<0.01	<0.001	<0.01	<0.01	16.59	0.04	<0.001	0.06	0.41
633118	Drill Core	1.41	0.002	0.002	0.09	1.11	<2	0.006	<0.001	0.02	1.03	<0.02	<0.01	0.003	<0.01	<0.01	8.79	0.10	0.001	0.10	0.74
633119	Drill Core	2.59	<0.001	0.003	0.04	0.09	<2	0.003	<0.001	0.04	0.28	<0.02	0.02	<0.001	<0.01	<0.01	29.85	0.03	<0.001	0.09	0.44
633120	Rock	0.37	<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	0.02	0.09	<0.02	0.01	<0.001	<0.01	<0.01	20.84	0.03	<0.001	11.33	0.10
633121	Drill Core	2.55	0.001	0.002	0.17	0.30	<2	0.005	<0.001	0.01	0.45	<0.02	<0.01	<0.001	<0.01	<0.01	7.54	0.04	<0.001	0.06	0.44
633122	Drill Core	1.01	0.002	0.004	0.33	3.96	<2	0.007	<0.001	<0.01	0.54	<0.02	<0.01	0.009	<0.01	<0.01	3.97	0.17	0.002	0.10	0.67
633123	Drill Core	1.94	0.002	0.003	0.15	0.96	<2	0.007	<0.001	0.03	1.40	<0.02	<0.01	0.002	<0.01	<0.01	12.67	0.29	0.001	0.09	0.44
633124	Drill Core	0.55	0.004	0.012	0.29	3.08	2	0.011	<0.001	0.03	1.77	<0.02	0.01	0.009	<0.01	<0.01	14.08	0.45	0.002	0.12	0.87
633125	Drill Core	3.62	0.003	0.009	0.03	0.17	<2	0.006	<0.001	0.03	0.79	<0.02	0.01	<0.001	<0.01	<0.01	22.17	0.50	0.001	0.09	0.34
633126	Drill Core	2.64	0.002	0.004	0.09	0.44	<2	0.005	<0.001	0.03	1.52	<0.02	0.01	0.001	<0.01	<0.01	21.09	0.31	0.002	0.08	0.35
633127	Drill Core	1.65	0.003	0.008	0.30	1.26	2	0.008	<0.001	0.03	0.73	<0.02	0.02	0.004	<0.01	<0.01	21.84	0.45	0.002	0.11	0.69
633128	Drill Core	1.87	0.006	0.019	0.27	0.65	4	0.013	<0.001	<0.01	3.93	<0.02	<0.01	0.002	<0.01	<0.01	5.74	0.25	0.004	0.12	1.00
633129	Drill Core	2.98	0.008	0.021	0.17	0.64	3	0.019	<0.001	<0.01	4.33	<0.02	<0.01	0.002	<0.01	<0.01	5.58	0.38	0.006	0.16	1.31
633130	Rock Pulp	0.14	0.002	0.832	0.93	1.31	226	0.002	0.002	0.23	2.74	0.02	0.01	0.009	0.02	<0.01	1.99	0.01	0.003	0.13	1.33



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: December 16, 2010

Page: 2 of 3 **Part** 2

CERTIFICATE OF ANALYSIS

WHI10000653.1

	Method	7TD	7TD	7TD	7TD	G8SG
	Analyte	Na	K	W	S	SG
	Unit	%	%	%	%	
	MDL	0.01	0.01	0.01	0.05	0
633101	Drill Core	0.05	0.98	<0.01	1.96	2.30
633102	Drill Core	0.04	0.20	<0.01	0.83	2.42
633103	Drill Core	0.12	0.42	<0.01	1.02	2.37
633104	Drill Core	0.04	0.19	<0.01	3.52	2.55
633105	Drill Core	<0.01	0.28	<0.01	6.65	2.56
633106	Drill Core	<0.01	0.28	<0.01	2.40	2.45
633107	Drill Core	<0.01	0.38	<0.01	5.20	2.64
633108	Drill Core	<0.01	0.12	<0.01	5.29	2.60
633109	Drill Core	<0.01	0.38	<0.01	1.96	2.46
633110	Drill Core	<0.01	0.27	<0.01	1.53	2.51
633111	Drill Core	<0.01	0.31	<0.01	1.37	2.57
633112	Drill Core	<0.01	0.34	<0.01	0.58	2.39
633113	Drill Core	<0.01	0.23	<0.01	0.65	2.48
633114	Drill Core	<0.01	0.37	<0.01	1.22	2.47
633115	Drill Core	<0.01	0.48	<0.01	0.76	2.37
633116	Drill Core	<0.01	0.16	<0.01	0.23	2.41
633117	Drill Core	<0.01	0.21	<0.01	1.51	2.46
633118	Drill Core	<0.01	0.44	<0.01	1.58	2.36
633119	Drill Core	<0.01	0.22	<0.01	0.33	2.56
633120	Rock	<0.01	0.02	<0.01	<0.05	2.63
633121	Drill Core	<0.01	0.25	<0.01	0.58	2.39
633122	Drill Core	<0.01	0.36	<0.01	2.52	2.42
633123	Drill Core	<0.01	0.25	<0.01	2.04	2.41
633124	Drill Core	<0.01	0.47	<0.01	3.47	2.34
633125	Drill Core	<0.01	0.17	<0.01	0.97	2.34
633126	Drill Core	<0.01	0.18	<0.01	1.96	2.40
633127	Drill Core	<0.01	0.36	<0.01	1.44	2.36
633128	Drill Core	<0.01	0.57	<0.01	5.02	2.28
633129	Drill Core	<0.01	0.75	<0.01	5.32	2.16
633130	Rock Pulp	0.57	0.28	<0.01	2.05	N.A.



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: December 16, 2010

Page: 3 of 3 **Part** 1

CERTIFICATE OF ANALYSIS

WHI10000653.1

	Method Analyte Unit MDL	WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD
		Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg
		kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%
		0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01
633131	Drill Core	1.90	0.011	0.018	0.14	0.35	4	0.025	<0.001	<0.01	1.41	<0.02	<0.01	0.001	<0.01	<0.01	5.89	1.30	0.010	0.21
633132	Drill Core	2.46	0.007	0.007	0.03	1.19	2	0.018	<0.001	<0.01	2.08	<0.02	<0.01	0.007	<0.01	<0.01	2.11	0.36	0.007	0.29
633133	Drill Core	2.25	0.007	0.005	<0.02	0.26	<2	0.018	<0.001	<0.01	2.15	<0.02	<0.01	0.002	<0.01	<0.01	2.01	0.08	0.008	0.35
633134	Drill Core	1.91	0.007	0.007	<0.02	<0.01	<2	0.018	<0.001	0.01	2.46	<0.02	<0.01	0.002	<0.01	<0.01	3.54	0.06	0.008	0.38



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: December 16, 2010

Page: 3 of 3 **Part** 2

CERTIFICATE OF ANALYSIS

WHI10000653.1

	Method	7TD	7TD	7TD	7TD	G8SG
	Analyte	Na	K	W	S	SG
	Unit	%	%	%	%	
	MDL	0.01	0.01	0.01	0.05	0
633131	Drill Core	<0.01	1.22	<0.01	1.72	1.98
633132	Drill Core	0.01	2.60	<0.01	2.82	2.14
633133	Drill Core	0.01	3.43	<0.01	2.50	2.10
633134	Drill Core	<0.01	3.35	<0.01	2.72	2.13



Acme Analytical Laboratories (Vancouver) Ltd.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: **Selwyn Resources Ltd.**

Suite 700 - 509 Richards Street

Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: December 16, 2010

Page: 1 of 2 Part 1

QUALITY CONTROL REPORT

WHI10000653.1

	Method Analyte Unit MDL	WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD
		Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg	Al
		kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%	%
		0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01	0.01
Pulp Duplicates																					
633132	Drill Core	2.46	0.007	0.007	0.03	1.19	2	0.018	<0.001	<0.01	2.08	<0.02	<0.01	0.007	<0.01	<0.01	2.11	0.36	0.007	0.29	3.52
REP 633132	QC		0.007	0.006	0.03	1.18	2	0.018	<0.001	<0.01	2.02	<0.02	<0.01	0.007	<0.01	<0.01	2.12	0.34	0.006	0.28	3.50
Core Reject Duplicates																					
DUP G1	QC		<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	0.07	2.27	<0.02	0.07	<0.001	<0.01	<0.01	2.33	0.07	<0.001	0.56	6.29
633134	Drill Core	1.91	0.007	0.007	<0.02	<0.01	<2	0.018	<0.001	0.01	2.46	<0.02	<0.01	0.002	<0.01	<0.01	3.54	0.06	0.008	0.38	4.30
DUP 633134	QC		0.006	0.007	<0.02	<0.01	<2	0.018	<0.001	0.01	2.32	<0.02	<0.01	<0.001	<0.01	<0.01	3.63	0.06	0.008	0.36	4.27
Reference Materials																					
STD OREAS131A	Standard		<0.001	0.031	1.61	2.84	30	0.002	0.002	0.17	5.65	<0.02	<0.01	0.008	<0.01	<0.01	5.25	0.06	0.002	3.11	4.52
STD OREAS131A	Standard		0.001	0.032	1.63	2.84	31	0.002	0.002	0.17	5.81	<0.02	<0.01	0.008	<0.01	<0.01	5.32	0.05	0.003	3.05	4.50
STD OREAS131A	Standard		<0.001	0.033	1.71	2.85	31	0.003	0.002	0.18	5.91	<0.02	<0.01	0.008	<0.01	<0.01	5.45	0.06	0.002	3.15	4.69
STD OREAS131A	Standard		<0.001	0.032	1.70	2.87	31	0.003	0.002	0.17	5.78	<0.02	<0.01	0.008	<0.01	<0.01	5.28	0.05	0.003	3.14	4.65
STD R4T	Standard		0.062	0.502	1.54	3.42	88	0.351	0.040	0.09	24.20	<0.02	0.02	0.019	0.01	<0.01	2.19	0.05	0.018	1.43	3.97
STD R4T	Standard		0.062	0.504	1.47	3.39	86	0.346	0.040	0.09	24.13	<0.02	0.02	0.019	0.02	<0.01	2.18	0.04	0.013	1.38	3.84
STD R4T	Standard		0.064	0.517	1.54	3.46	86	0.355	0.043	0.09	24.13	<0.02	0.02	0.020	0.01	<0.01	2.21	0.04	0.019	1.43	4.02
STD R4T	Standard		0.064	0.513	1.57	3.48	89	0.356	0.041	0.09	24.19	<0.02	0.02	0.019	0.01	<0.01	2.21	0.04	0.018	1.43	3.99
STD SU-1B	Standard		<0.001	1.158	<0.02	0.03	7	1.956	0.065	0.07	25.15	<0.02	0.03	<0.001	<0.01	<0.01	2.22	0.06	0.028	1.79	4.38
STD SU-1B	Standard		<0.001	1.183	<0.02	0.03	7	1.977	0.068	0.07	25.76	<0.02	0.03	<0.001	<0.01	<0.01	2.29	0.07	0.030	1.80	4.35
STD SU-1B	Standard		<0.001	1.182	<0.02	0.03	6	2.020	0.069	0.07	25.32	<0.02	0.03	0.002	<0.01	<0.01	2.25	0.06	0.033	1.81	4.47
STD SU-1B	Standard		<0.001	1.169	<0.02	0.03	6	1.963	0.066	0.07	25.02	<0.02	0.03	<0.001	<0.01	<0.01	2.22	0.06	0.031	1.80	4.41
STD R4T Expected			0.062	0.502	1.518	3.376	86	0.339	0.039	0.086	24.07	0.0087	0.0185	0.018	0.0138	0.0018	2.166	0.045	0.018	1.384	3.897
STD OREAS131A Expected			0.001	0.0322	1.72	2.83	30.9	0.0027	0.0023	0.1722	5.8166	0.0082	0.0028	0.0081	0.0047	0.001	5.286	0.0536	0.0025	3.1182	4.6057
STD SU-1B Expected			0.0004	1.185	0.0058	0.0235	6.4	1.97	0.0672	0.0703	25.54	0.00025	0.03	0.0003	0.00002	0.0003	2.21	0.06	0.032	1.79	4.39
BLK	Blank		<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	<0.01	<0.01	<0.02	<0.01	<0.001	<0.01	<0.01	<0.01	<0.01	<0.001	<0.01	<0.01
BLK	Blank		<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	<0.01	<0.01	<0.02	<0.01	<0.001	<0.01	<0.01	<0.01	<0.01	<0.001	<0.01	<0.01
BLK	Blank		<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	<0.01	<0.01	<0.02	<0.01	<0.001	<0.01	<0.01	<0.01	<0.01	<0.001	<0.01	<0.01
BLK	Blank		<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	<0.01	<0.01	<0.02	<0.01	<0.001	<0.01	<0.01	<0.01	<0.01	<0.001	<0.01	<0.01
Prep Wash																					
G1	Prep Blank		<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	0.07	2.35	<0.02	0.07	<0.001	<0.01	<0.01	2.44	0.08	<0.001	0.58	6.42



Acme Analytical Laboratories (Vancouver) Ltd.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: **Selwyn Resources Ltd.**

Suite 700 - 509 Richards Street

Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: December 16, 2010

Page: 1 of 2 **Part** 2

QUALITY CONTROL REPORT

WHI10000653.1

Method		7TD	7TD	7TD	7TD	G8SG
Analyte		Na	K	W	S	SG
Unit		%	%	%	%	%
MDL		0.01	0.01	0.01	0.05	0
Pulp Duplicates						
633132	Drill Core	0.01	2.60	<0.01	2.82	2.14
REP 633132	QC	0.01	2.52	<0.01	2.70	
Core Reject Duplicates						
DUP G1	QC	2.73	2.80	<0.01	<0.05	2.63
633134	Drill Core	<0.01	3.35	<0.01	2.72	2.13
DUP 633134	QC	0.02	3.35	<0.01	2.45	2.16
Reference Materials						
STD OREAS131A	Standard	0.15	3.39	<0.01	4.69	
STD OREAS131A	Standard	0.15	3.41	<0.01	4.74	
STD OREAS131A	Standard	0.15	3.41	<0.01	4.98	
STD OREAS131A	Standard	0.15	3.38	<0.01	4.63	
STD R4T	Standard	0.92	1.19	<0.01	11.99	
STD R4T	Standard	0.92	1.17	<0.01	14.85	
STD R4T	Standard	0.92	1.26	<0.01	12.80	
STD R4T	Standard	0.91	1.18	<0.01	13.01	
STD SU-1B	Standard	1.68	0.61	<0.01	9.12	
STD SU-1B	Standard	1.72	0.64	<0.01	11.88	
STD SU-1B	Standard	1.71	0.63	<0.01	8.71	
STD SU-1B	Standard	1.67	0.61	<0.01	9.01	
STD R4T Expected		0.9	1.153	0.00016	12.9903	
STD OREAS131A Expected		0.1501	3.1584	0.0005	4.8	
STD SU-1B Expected		1.662	0.6	0.0007	8.76	
BLK	Blank	<0.01	<0.01	<0.01	<0.05	
BLK	Blank	<0.01	<0.01	<0.01	<0.05	
BLK	Blank	<0.01	<0.01	<0.01	<0.05	
BLK	Blank	<0.01	<0.01	<0.01	<0.05	
Prep Wash						
G1	Prep Blank	2.71	2.84	<0.01	<0.05	2.62



Acme Analytical Laboratories (Vancouver) Ltd.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: **Selwyn Resources Ltd.**

Suite 700 - 509 Richards Street

Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: December 16, 2010

Page: 2 of 2 **Part** 1

QUALITY CONTROL REPORT

WHI10000653.1

		WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD
		Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg
		kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%
		0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01
G1	Prep Blank		<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	0.07	2.26	<0.02	0.07	<0.001	<0.01	<0.01	2.34	0.07	<0.001	0.56



Acme Analytical Laboratories (Vancouver) Ltd.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: **Selwyn Resources Ltd.**

Suite 700 - 509 Richards Street

Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: December 16, 2010

Page: 2 of 2 **Part** 2

QUALITY CONTROL REPORT

WHI10000653.1

		7TD	7TD	7TD	7TD	G8SG
		Na	K	W	S	SG
		%	%	%	%	
		0.01	0.01	0.01	0.05	0
G1	Prep Blank	2.70	2.84	<0.01	<0.05	2.63



1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**

Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Submitted By: Jason K. Dunning

Receiving Lab: Canada-Whitehorse

Received: November 15, 2010

Report Date: December 10, 2010

Page: 1 of 3

CERTIFICATE OF ANALYSIS

WHI10000652.1

CLIENT JOB INFORMATION

Project: Selwyn Project
Shipment ID:
P.O. Number 1034
Number of Samples: 34

SAMPLE DISPOSAL

STOR-PLP Store After 90 days Invoice for Storage
STOR-RJT Store After 90 days Invoice for Storage

Acme does not accept responsibility for samples left at the laboratory after 90 days without prior written instructions for sample storage or return.

Invoice To: Selwyn Resources Ltd.
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6
Canada

CC:

SAMPLE PREPARATION AND ANALYTICAL PROCEDURES

Method Code	Number of Samples	Code Description	Test Wgt (g)	Report Status	Lab
R200-250	33	Crush split and pulverize 250g drill core to 200 mesh			WHI
7TD2	34	4 Acid digestion ICP-ES analysis.	0.5	Completed	VAN
G812	34	Specific Gravity on Pulp		Completed	VAN

ADDITIONAL COMMENTS



This report supersedes all previous preliminary and final reports with this file number dated prior to the date on this certificate. Signature indicates final approval; preliminary reports are unsigned and should be used for reference only.
All results are considered the confidential property of the client. Acme assumes the liabilities for actual cost of analysis only.
** asterisk indicates that an analytical result could not be provided due to unusually high levels of interference from other elements.



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: December 10, 2010

Page: 2 of 3 Part 1

CERTIFICATE OF ANALYSIS

WHI10000652.1

	Method Analyte Unit MDL	WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD
		Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg	Al
		kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%	%
		0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01	0.01
633501	Drill Core	1.31	0.002	0.008	0.05	0.38	<2	0.011	<0.001	<0.01	2.33	<0.02	<0.01	0.001	<0.01	<0.01	1.79	0.67	0.002	0.16	1.62
633502	Drill Core	1.21	0.004	0.010	0.44	0.40	2	0.013	<0.001	<0.01	3.78	<0.02	<0.01	0.002	<0.01	<0.01	1.46	0.47	0.003	0.18	1.81
633503	Drill Core	1.76	0.002	0.016	6.89	6.31	6	0.007	<0.001	0.01	6.10	<0.02	<0.01	0.037	<0.01	<0.01	0.25	0.02	<0.001	0.07	0.68
633504	Drill Core	2.77	0.002	0.011	2.73	7.70	3	0.006	<0.001	0.01	4.45	<0.02	<0.01	0.042	<0.01	<0.01	0.15	0.02	<0.001	0.07	0.84
633505	Drill Core	2.28	0.001	0.007	5.56	3.36	3	0.004	<0.001	<0.01	2.01	<0.02	<0.01	0.022	<0.01	<0.01	1.75	0.03	<0.001	0.08	0.77
633506	Drill Core	0.67	0.004	0.005	0.50	2.50	<2	0.008	<0.001	<0.01	2.36	<0.02	<0.01	0.012	<0.01	<0.01	0.96	0.03	0.001	0.12	1.27
633507	Drill Core	1.83	0.004	0.008	1.91	6.37	2	0.008	<0.001	0.01	4.35	<0.02	<0.01	0.030	<0.01	<0.01	0.40	0.04	0.001	0.07	0.81
633508	Drill Core	1.57	0.005	0.011	2.39	7.10	3	0.011	<0.001	0.02	8.26	<0.02	<0.01	0.025	<0.01	<0.01	2.55	0.06	0.002	0.13	1.62
633509	Drill Core	1.33	0.001	0.007	3.97	13.18	3	0.003	<0.001	<0.01	5.45	<0.02	<0.01	0.067	<0.01	<0.01	0.15	0.01	<0.001	0.04	0.36
633510	Drill Core	0.86	0.004	0.007	0.94	5.62	<2	0.009	<0.001	0.01	5.80	<0.02	<0.01	0.017	<0.01	<0.01	0.74	0.04	0.002	0.08	0.92
633511	Drill Core	0.81	0.003	0.007	0.80	5.15	<2	0.009	<0.001	0.01	7.18	<0.02	<0.01	0.016	<0.01	<0.01	1.37	0.03	0.002	0.08	0.84
633512	Drill Core	1.77	0.004	0.008	1.37	8.62	<2	0.008	<0.001	0.02	4.75	<0.02	<0.01	0.023	<0.01	<0.01	1.09	0.07	0.001	0.09	1.07
633513	Drill Core	2.86	0.001	0.001	0.14	0.72	<2	0.003	<0.001	0.04	0.67	<0.02	<0.01	0.002	<0.01	<0.01	17.52	0.08	<0.001	0.10	0.49
633514	Drill Core	0.77	0.005	0.009	3.41	6.35	<2	0.009	<0.001	0.03	3.81	<0.02	<0.01	0.019	<0.01	<0.01	6.98	0.05	0.002	0.09	0.98
633515	Drill Core	1.07	0.001	0.002	0.25	1.18	<2	0.003	<0.001	0.05	0.96	<0.02	0.01	0.004	<0.01	<0.01	24.61	0.05	0.001	0.23	0.47
633516	Drill Core	1.17	0.001	0.002	0.50	0.96	<2	0.007	<0.001	0.03	1.63	<0.02	<0.01	0.003	<0.01	<0.01	9.14	0.13	0.002	0.13	0.91
633517	Drill Core	2.06	0.001	0.003	1.39	4.24	<2	0.005	<0.001	0.03	2.13	<0.02	<0.01	0.012	<0.01	<0.01	11.87	0.06	<0.001	0.08	0.59
633518	Drill Core	2.29	0.002	0.003	0.82	5.42	<2	0.003	<0.001	0.04	2.42	<0.02	0.01	0.016	<0.01	<0.01	23.85	0.04	<0.001	0.08	0.34
633519	Drill Core	2.72	0.002	0.005	0.86	3.97	<2	0.007	<0.001	0.03	2.90	<0.02	<0.01	0.012	<0.01	<0.01	8.41	0.07	0.001	0.12	0.88
633520	Rock	0.47	<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	0.02	0.10	<0.02	<0.01	<0.001	<0.01	<0.01	21.35	0.02	<0.001	11.60	0.03
633521	Drill Core	1.08	0.001	0.003	1.38	2.89	<2	0.005	<0.001	0.03	2.97	<0.02	0.01	0.010	<0.01	<0.01	18.02	0.03	<0.001	0.11	0.45
633522	Drill Core	1.83	0.002	0.008	2.48	11.85	3	0.007	<0.001	0.02	3.97	<0.02	<0.01	0.034	<0.01	<0.01	6.28	0.05	0.001	0.09	0.69
633523	Drill Core	1.76	0.002	0.002	0.57	1.50	<2	0.005	<0.001	0.02	0.84	<0.02	<0.01	0.005	<0.01	<0.01	9.46	0.07	0.001	0.11	0.75
633524	Drill Core	2.19	<0.001	<0.001	<0.02	0.03	<2	0.001	<0.001	0.04	0.62	<0.02	0.01	<0.001	<0.01	<0.01	34.10	0.02	<0.001	0.07	0.13
633525	Drill Core	1.96	0.002	0.002	0.19	0.99	<2	0.006	<0.001	0.02	0.96	<0.02	<0.01	0.003	<0.01	<0.01	15.39	0.08	0.001	0.14	0.94
633526	Drill Core	1.96	<0.001	0.003	0.13	0.15	<2	0.004	<0.001	0.04	1.25	<0.02	0.01	<0.001	<0.01	<0.01	28.68	0.04	0.001	0.09	0.45
633527	Drill Core	1.41	0.001	0.004	0.85	0.10	<2	0.006	<0.001	0.03	1.85	<0.02	0.01	<0.001	<0.01	<0.01	18.02	0.05	0.002	0.11	0.81
633528	Drill Core	0.50	<0.001	0.003	0.03	0.01	<2	0.004	<0.001	0.02	2.40	<0.02	<0.01	<0.001	<0.01	<0.01	9.28	0.02	<0.001	0.05	0.31
633529	Drill Core	3.09	0.001	0.005	0.04	0.12	<2	0.005	<0.001	0.02	2.00	<0.02	<0.01	<0.001	<0.01	<0.01	10.17	0.05	<0.001	0.09	0.52
633530	Rock Pulp	0.15	<0.001	0.484	1.43	4.32	27	0.001	0.001	0.66	5.38	<0.02	0.01	0.027	<0.01	<0.01	4.09	0.05	0.003	1.51	4.56



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: December 10, 2010

Page: 2 of 3 **Part** 2

CERTIFICATE OF ANALYSIS

WHI10000652.1

	Method	7TD	7TD	7TD	7TD	G8SG
Analyte	Na	K	W	S	SG	
Unit	%	%	%	%		
MDL	0.01	0.01	0.01	0.05	0	
633501	Drill Core	<0.01	1.02	<0.01	2.71	2.31
633502	Drill Core	0.02	1.12	<0.01	4.41	2.27
633503	Drill Core	<0.01	0.40	<0.01	11.11	2.70
633504	Drill Core	<0.01	0.50	<0.01	9.24	2.61
633505	Drill Core	<0.01	0.49	<0.01	4.49	2.62
633506	Drill Core	<0.01	0.80	<0.01	3.67	2.38
633507	Drill Core	<0.01	0.49	<0.01	8.48	2.55
633508	Drill Core	<0.01	1.09	<0.01	13.31	2.58
633509	Drill Core	<0.01	0.19	<0.01	13.12	2.81
633510	Drill Core	<0.01	0.58	<0.01	9.57	2.51
633511	Drill Core	<0.01	0.53	<0.01	10.95	2.58
633512	Drill Core	<0.01	0.72	<0.01	9.90	2.52
633513	Drill Core	<0.01	0.31	<0.01	1.07	2.40
633514	Drill Core	<0.01	0.66	<0.01	8.10	2.58
633515	Drill Core	<0.01	0.29	<0.01	1.57	2.50
633516	Drill Core	<0.01	0.58	<0.01	2.24	2.44
633517	Drill Core	<0.01	0.39	<0.01	4.60	2.53
633518	Drill Core	<0.01	0.21	<0.01	5.71	2.63
633519	Drill Core	<0.01	0.53	<0.01	5.21	2.51
633520	Rock	<0.01	0.02	<0.01	<0.05	2.61
633521	Drill Core	<0.01	0.27	<0.01	5.05	2.61
633522	Drill Core	<0.01	0.41	<0.01	10.69	2.87
633523	Drill Core	<0.01	0.45	<0.01	1.65	2.45
633524	Drill Core	<0.01	0.10	<0.01	0.69	2.52
633525	Drill Core	<0.01	0.57	<0.01	1.51	2.48
633526	Drill Core	<0.01	0.36	<0.01	1.57	2.56
633527	Drill Core	<0.01	0.44	<0.01	2.38	2.47
633528	Drill Core	<0.01	0.40	<0.01	2.92	2.58
633529	Drill Core	<0.01	0.31	<0.01	2.37	2.48
633530	Rock Pulp	0.09	3.26	<0.01	5.18	N.A.



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: December 10, 2010

Page: 3 of 3 **Part** 1

CERTIFICATE OF ANALYSIS

WHI10000652.1

	Method	WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD
	Analyte	Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg	Al
	Unit	kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%	%
	MDL	0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01	0.01
633531	Drill Core	2.49	0.003	0.010	0.13	0.58	<2	0.007	<0.001	0.03	4.06	<0.02	0.01	0.002	<0.01	<0.01	17.24	0.22	0.002	0.12	0.49
633532	Drill Core	0.82	0.006	0.019	0.16	1.20	2	0.011	<0.001	0.02	1.10	<0.02	0.01	0.004	<0.01	<0.01	10.22	0.29	0.003	0.13	0.82
633533	Drill Core	2.21	0.004	0.010	0.06	0.25	<2	0.022	<0.001	<0.01	2.47	<0.02	<0.01	0.001	<0.01	<0.01	3.41	0.46	0.010	0.37	3.80
633534	Drill Core	1.96	0.002	0.009	<0.02	0.01	<2	0.019	<0.001	<0.01	2.59	<0.02	<0.01	0.001	<0.01	<0.01	3.01	0.55	0.011	0.34	4.57



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: December 10, 2010

Page: 3 of 3 **Part** 2

CERTIFICATE OF ANALYSIS

WHI10000652.1

		Method	7TD	7TD	7TD	7TD	G8SG
		Analyte	Na	K	W	S	SG
		Unit	%	%	%	%	
		MDL	0.01	0.01	0.01	0.05	0
633531	Drill Core		<0.01	0.28	<0.01	5.50	2.51
633532	Drill Core		0.08	0.46	<0.01	1.88	2.35
633533	Drill Core		0.16	2.52	<0.01	3.03	2.26
633534	Drill Core		0.03	3.59	<0.01	2.95	2.39



Acme Analytical Laboratories (Vancouver) Ltd.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: Selwyn Resources Ltd.

Suite 700 - 509 Richards Street

Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: December 10, 2010

Page: 1 of 1 Part 1

QUALITY CONTROL REPORT

WHI10000652.1

	Method Analyte Unit MDL	WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD
		Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg	Al
		kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%	%
		0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.01	0.001	0.01
Pulp Duplicates																					
633511	Drill Core	0.81	0.003	0.007	0.80	5.15	<2	0.009	<0.001	0.01	7.18	<0.02	<0.01	0.016	<0.01	<0.01	1.37	0.03	0.002	0.08	0.84
REP 633511	QC		0.004	0.007	0.79	5.11	<2	0.009	<0.001	0.01	7.09	<0.02	<0.01	0.016	<0.01	<0.01	1.37	0.04	0.002	0.07	0.83
Core Reject Duplicates																					
633520	Rock	0.47	<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	0.02	0.10	<0.02	<0.01	<0.001	<0.01	<0.01	21.35	0.02	<0.001	11.60	0.03
DUP 633520	QC		<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	0.02	0.10	<0.02	<0.01	<0.001	<0.01	<0.01	21.33	0.02	<0.001	11.66	0.03
Reference Materials																					
STD OREAS131A	Standard		<0.001	0.032	1.71	2.90	31	0.003	0.002	0.17	5.81	<0.02	<0.01	0.008	<0.01	<0.01	5.37	0.05	0.002	3.15	4.65
STD OREAS131A	Standard		<0.001	0.033	1.71	2.85	31	0.003	0.002	0.18	5.91	<0.02	<0.01	0.008	<0.01	<0.01	5.45	0.06	0.002	3.15	4.69
STD R4T	Standard		0.064	0.510	1.56	3.47	89	0.355	0.041	0.09	24.19	<0.02	0.02	0.019	0.02	<0.01	2.22	0.05	0.019	1.43	3.99
STD R4T	Standard		0.064	0.517	1.54	3.46	86	0.355	0.043	0.09	24.13	<0.02	0.02	0.020	0.01	<0.01	2.21	0.04	0.019	1.43	4.02
STD SU-1B	Standard		<0.001	1.151	<0.02	0.03	6	1.969	0.066	0.07	25.20	<0.02	0.03	<0.001	<0.01	<0.01	2.23	0.06	0.031	1.80	4.39
STD SU-1B	Standard		<0.001	1.182	<0.02	0.03	6	2.020	0.069	0.07	25.32	<0.02	0.03	0.002	<0.01	<0.01	2.25	0.06	0.033	1.81	4.47
STD R4T Expected			0.062	0.502	1.518	3.376	86	0.339	0.039	0.086	24.07	0.0087	0.0185	0.018	0.0138	0.0018	2.166	0.045	0.018	1.384	3.897
STD OREAS131A Expected			0.001	0.0322	1.72	2.83	30.9	0.0027	0.0023	0.1722	5.8166	0.0082	0.0028	0.0081	0.0047	0.001	5.286	0.0536	0.0025	3.1182	4.6057
STD SU-1B Expected			0.0004	1.185	0.0058	0.0235	6.4	1.97	0.0672	0.0703	25.54	0.00025	0.03	0.0003	0.00002	0.0003	2.21	0.06	0.032	1.79	4.39
BLK	Blank		<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	<0.01	<0.01	<0.02	<0.01	<0.001	<0.01	<0.01	<0.01	<0.01	<0.001	<0.01	<0.01
BLK	Blank		<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	<0.01	<0.01	<0.02	<0.01	<0.001	<0.01	<0.01	<0.01	<0.01	<0.001	<0.01	<0.01
Prep Wash																					
G1	Prep Blank		<0.001	0.002	<0.02	<0.01	<2	<0.001	<0.001	0.07	2.28	<0.02	0.08	<0.001	<0.01	<0.01	2.39	0.08	<0.001	0.55	7.95
G1	Prep Blank		<0.001	0.001	<0.02	<0.01	<2	<0.001	<0.001	0.07	2.29	<0.02	0.08	<0.001	<0.01	<0.01	2.38	0.08	<0.001	0.55	8.03



Acme Analytical Laboratories (Vancouver) Ltd.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: **Selwyn Resources Ltd.**

Suite 700 - 509 Richards Street

Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: December 10, 2010

Page: 1 of 1 Part 2

QUALITY CONTROL REPORT

WHI10000652.1

		Method	7TD	7TD	7TD	7TD	G8SG
		Analyte	Na	K	W	S	SG
		Unit	%	%	%	%	
		MDL	0.01	0.01	0.01	0.05	0
Pulp Duplicates							
633511	Drill Core		<0.01	0.53	<0.01	10.95	2.58
REP 633511	QC		<0.01	0.52	<0.01	10.83	
Core Reject Duplicates							
633520	Rock		<0.01	0.02	<0.01	<0.05	2.61
DUP 633520	QC		<0.01	0.02	<0.01	<0.05	2.59
Reference Materials							
STD OREAS131A	Standard		0.16	3.25	<0.01	4.80	
STD OREAS131A	Standard		0.15	3.41	<0.01	4.98	
STD R4T	Standard		0.93	1.19	<0.01	12.16	
STD R4T	Standard		0.92	1.26	<0.01	12.80	
STD SU-1B	Standard		1.67	0.61	<0.01	8.14	
STD SU-1B	Standard		1.71	0.63	<0.01	8.71	
STD R4T Expected			0.9	1.153	0.00016	12.9903	
STD OREAS131A Expected			0.1501	3.1584	0.0005	4.8	
STD SU-1B Expected			1.662	0.6	0.0007	8.76	
BLK	Blank		<0.01	<0.01	<0.01	<0.05	
BLK	Blank		<0.01	<0.01	<0.01	<0.05	
Prep Wash							
G1	Prep Blank		2.85	2.55	<0.01	<0.05	2.65
G1	Prep Blank		2.84	2.31	<0.01	<0.05	2.68



1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: Selwyn Resources Ltd.

Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Submitted By: Jason K. Dunning

Receiving Lab: Canada-Whitehorse

Received: November 12, 2010

Report Date: November 30, 2010

Page: 1 of 3

CERTIFICATE OF ANALYSIS

WHI10000650.1

CLIENT JOB INFORMATION

Project: Selwyn Project
Shipment ID:
P.O. Number: 1024
Number of Samples: 57

SAMPLE DISPOSAL

STOR-PLP Store After 90 days Invoice for Storage
STOR-RJT Store After 90 days Invoice for Storage

Acme does not accept responsibility for samples left at the laboratory after 90 days without prior written instructions for sample storage or return.

Invoice To: Selwyn Resources Ltd.
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6
Canada

CC:

SAMPLE PREPARATION AND ANALYTICAL PROCEDURES

Method Code	Number of Samples	Code Description	Test Wgt (g)	Report Status	Lab
R200-250	56	Crush split and pulverize 250g drill core to 200 mesh			WHI
7TD2	57	4 Acid digestion ICP-ES analysis.	0.5	Completed	VAN
7TD.1	1	4 Acid digestion ICP-ES analysis	0.1	Completed	VAN
G812	57	Specific Gravity on Pulp		Completed	VAN

ADDITIONAL COMMENTS



This report supersedes all previous preliminary and final reports with this file number dated prior to the date on this certificate. Signature indicates final approval; preliminary reports are unsigned and should be used for reference only.
All results are considered the confidential property of the client. Acme assumes the liabilities for actual cost of analysis only.
** asterisk indicates that an analytical result could not be provided due to unusually high levels of interference from other elements.



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: November 30, 2010

Page: 2 of 3 Part 1

CERTIFICATE OF ANALYSIS

WHI10000650.1

	Method Analyte Unit MDL	WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD
		Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg	Al
		kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%	%
		0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01	0.01
631451	Drill Core	1.87	0.004	0.009	0.04	0.39	2	0.014	<0.001	<0.01	1.24	<0.02	<0.01	0.002	<0.01	<0.01	3.10	1.39	0.007	0.26	2.38
631452	Drill Core	1.53	0.001	0.004	<0.02	0.43	<2	0.009	<0.001	<0.01	0.74	<0.02	<0.01	0.002	<0.01	<0.01	2.30	0.90	0.003	0.15	1.46
631453	Drill Core	1.97	0.002	0.003	0.02	0.51	<2	0.008	<0.001	<0.01	0.74	<0.02	<0.01	0.003	<0.01	<0.01	2.83	0.26	0.002	0.12	1.15
631454	Drill Core	0.62	<0.001	0.002	<0.02	<0.01	<2	0.002	<0.001	0.09	0.54	<0.02	0.02	<0.001	<0.01	<0.01	32.74	0.02	<0.001	0.12	0.22
631455	Drill Core	0.54	0.001	0.005	1.31	2.03	<2	0.003	<0.001	0.09	2.55	<0.02	0.02	0.020	<0.01	<0.01	31.10	0.03	0.001	0.12	0.20
631456	Drill Core	1.17	<0.001	0.009	4.27	5.16	5	0.003	<0.001	0.06	1.52	<0.02	0.02	0.062	<0.01	<0.01	30.57	0.02	<0.001	0.14	0.21
631457	Drill Core	0.85	<0.001	0.001	1.10	1.20	<2	0.001	<0.001	0.07	0.56	<0.02	0.02	0.008	<0.01	<0.01	35.50	0.02	<0.001	0.11	0.15
631458	Drill Core	1.23	<0.001	0.002	6.89	4.96	4	0.001	<0.001	0.05	0.33	<0.02	0.01	0.035	<0.01	<0.01	23.80	0.02	<0.001	0.08	0.29
631459	Drill Core	0.90	<0.001	0.003	>10	8.86	4	0.003	<0.001	0.01	0.65	<0.02	<0.01	0.053	<0.01	<0.01	3.64	0.03	<0.001	0.06	0.69
631460	Drill Core	0.66	0.007	0.008	3.15	5.27	3	0.013	<0.001	0.02	4.11	<0.02	<0.01	0.023	<0.01	<0.01	0.77	0.08	0.003	0.16	2.14
631461	Drill Core	0.62	0.007	0.008	3.65	4.83	3	0.013	<0.001	0.01	4.11	<0.02	<0.01	0.021	<0.01	<0.01	0.50	0.07	0.003	0.18	2.22
631462	Drill Core	1.86	0.004	0.013	3.34	12.99	5	0.009	<0.001	0.02	6.98	<0.02	<0.01	0.054	<0.01	<0.01	0.41	0.04	0.002	0.08	0.99
631463	Drill Core	0.46	<0.001	0.011	9.76	14.31	5	0.001	<0.001	0.01	1.27	<0.02	<0.01	0.068	<0.01	<0.01	0.50	<0.01	<0.001	0.04	0.47
631464	Drill Core	1.77	0.004	0.008	1.26	5.37	2	0.009	<0.001	0.01	7.29	<0.02	<0.01	0.016	<0.01	<0.01	0.73	0.03	0.003	0.08	0.89
631465	Drill Core	1.32	0.003	0.006	1.51	6.94	2	0.008	<0.001	0.02	3.08	<0.02	<0.01	0.019	<0.01	<0.01	1.18	0.05	0.002	0.08	0.79
631466	Drill Core	1.24	0.002	0.005	0.60	5.56	<2	0.009	<0.001	0.01	2.82	<0.02	<0.01	0.013	<0.01	<0.01	1.40	0.06	0.002	0.10	0.93
631467	Drill Core	0.78	<0.001	<0.001	0.02	0.34	<2	<0.001	<0.001	0.16	0.32	<0.02	0.02	<0.001	<0.01	<0.01	36.31	0.04	<0.001	0.18	0.04
631468	Drill Core	1.56	0.005	0.010	1.00	9.75	2	0.011	<0.001	0.03	6.92	<0.02	<0.01	0.022	<0.01	<0.01	3.31	0.09	0.002	0.10	1.36
631469	Drill Core	1.19	0.001	0.002	0.61	3.36	<2	0.004	<0.001	0.03	1.52	<0.02	0.01	0.008	<0.01	<0.01	17.17	0.21	0.001	0.08	0.58
631470	Rock	0.38	<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	0.02	0.12	<0.02	0.01	<0.001	<0.01	<0.01	21.67	0.03	<0.001	10.46	0.10
631471	Drill Core	2.01	0.001	0.002	2.71	2.33	<2	0.004	<0.001	0.03	0.98	<0.02	0.01	0.007	<0.01	<0.01	15.74	0.05	0.002	0.09	0.60
631472	Drill Core	1.73	0.002	0.004	1.11	4.60	<2	0.006	<0.001	0.02	2.86	<0.02	<0.01	0.016	<0.01	<0.01	8.32	0.05	0.001	0.09	0.58
631473	Drill Core	0.92	0.003	0.012	2.85	12.26	2	0.005	<0.001	0.03	5.36	<0.02	<0.01	0.037	<0.01	<0.01	8.05	0.06	0.001	0.05	0.43
631474	Drill Core	1.39	<0.001	0.002	0.81	2.14	<2	0.002	<0.001	0.06	1.86	<0.02	0.02	0.006	<0.01	<0.01	28.19	0.04	<0.001	0.13	0.33
631475	Drill Core	1.57	<0.001	0.002	1.95	3.61	<2	0.003	<0.001	0.03	1.89	<0.02	0.01	0.012	<0.01	<0.01	18.89	0.09	0.001	0.09	0.52
631476	Drill Core	1.69	<0.001	0.002	0.95	2.29	<2	0.004	<0.001	0.04	2.25	<0.02	0.01	0.007	<0.01	<0.01	16.30	0.07	0.002	0.11	0.68
631477	Drill Core	2.12	0.001	0.003	1.30	5.12	<2	0.003	<0.001	0.05	1.82	<0.02	0.02	0.017	<0.01	<0.01	26.83	0.05	0.001	0.10	0.47
631478	Drill Core	2.06	<0.001	0.001	0.32	2.95	<2	0.002	<0.001	0.04	1.63	<0.02	0.02	0.008	<0.01	<0.01	29.58	0.04	<0.001	0.08	0.30
631479	Drill Core	1.53	0.002	0.004	1.61	7.62	<2	0.005	<0.001	0.03	2.89	<0.02	<0.01	0.020	<0.01	<0.01	12.79	0.05	<0.001	0.09	0.60
631480	Rock Pulp	0.02	<0.001	0.461	1.47	4.24	32	0.001	<0.001	0.69	5.54	<0.02	0.01	0.027	<0.01	<0.01	4.15	0.05	0.004	1.55	4.56



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: Selwyn Resources Ltd.

Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: November 30, 2010

Page: 2 of 3 Part 2

CERTIFICATE OF ANALYSIS

WHI10000650.1

	Method Analyte Unit MDL	7TD	7TD	7TD	7TD	7TD.1	G8SG
		Na	K	W	S	Pb	SG
		%	%	%	%	%	
		0.01	0.01	0.01	0.05	0.02	0
631451	Drill Core	<0.01	1.42	<0.01	1.62		2.20
631452	Drill Core	<0.01	0.92	<0.01	1.00		2.27
631453	Drill Core	<0.01	0.71	<0.01	1.02		2.28
631454	Drill Core	<0.01	0.11	<0.01	0.87		2.44
631455	Drill Core	<0.01	0.10	<0.01	4.64		2.53
631456	Drill Core	<0.01	0.10	<0.01	5.38		2.74
631457	Drill Core	<0.01	0.08	<0.01	1.69		2.60
631458	Drill Core	<0.01	0.15	<0.01	4.05		2.78
631459	Drill Core	<0.01	0.44	<0.01	6.40	9.64	2.83
631460	Drill Core	<0.01	1.46	<0.01	7.60		2.51
631461	Drill Core	<0.01	1.53	<0.01	7.26		2.54
631462	Drill Core	<0.01	0.66	<0.01	14.43		2.83
631463	Drill Core	<0.01	0.31	<0.01	9.22		3.03
631464	Drill Core	<0.01	0.55	<0.01	11.22		2.67
631465	Drill Core	<0.01	0.49	<0.01	7.06		2.57
631466	Drill Core	<0.01	0.55	<0.01	5.90		2.41
631467	Drill Core	<0.01	0.02	<0.01	0.85		2.66
631468	Drill Core	<0.01	0.91	<0.01	12.76		2.61
631469	Drill Core	<0.01	0.32	<0.01	3.67		2.55
631470	Rock	<0.01	0.01	<0.01	0.15		2.67
631471	Drill Core	<0.01	0.34	<0.01	2.76		2.57
631472	Drill Core	<0.01	0.34	<0.01	5.81		2.58
631473	Drill Core	<0.01	0.27	<0.01	12.58		2.82
631474	Drill Core	<0.01	0.16	<0.01	3.66		2.65
631475	Drill Core	<0.01	0.28	<0.01	4.51		2.62
631476	Drill Core	<0.01	0.39	<0.01	4.02		2.59
631477	Drill Core	<0.01	0.26	<0.01	5.20		2.65
631478	Drill Core	<0.01	0.16	<0.01	3.68		2.59
631479	Drill Core	<0.01	0.36	<0.01	7.64		2.71
631480	Rock Pulp	0.09	2.66	<0.01	4.99		N.A.



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: November 30, 2010

Page: 3 of 3 Part 1

CERTIFICATE OF ANALYSIS

WHI10000650.1

	Method Analyte Unit MDL	WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	
		Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg	Al
		kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%	%
		0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01	0.01
631481	Drill Core	1.94	0.002	0.003	0.40	2.01	<2	0.004	<0.001	0.04	1.84	<0.02	0.01	0.005	<0.01	<0.01	24.72	0.04	<0.001	0.10	0.47
631482	Drill Core	1.98	0.003	0.005	1.23	5.31	<2	0.008	<0.001	0.02	2.45	<0.02	<0.01	0.014	<0.01	<0.01	6.48	0.08	0.001	0.12	1.05
631483	Drill Core	1.35	0.002	0.004	2.62	5.99	<2	0.005	<0.001	0.02	1.57	<0.02	<0.01	0.016	<0.01	<0.01	7.44	0.34	<0.001	0.08	0.53
631484	Drill Core	2.09	0.001	0.002	0.76	1.16	<2	0.003	<0.001	0.03	1.69	<0.02	0.01	0.004	<0.01	<0.01	21.30	0.19	<0.001	0.09	0.38
631485	Drill Core	1.01	0.001	0.002	0.15	0.02	<2	0.005	<0.001	0.03	1.57	<0.02	0.01	<0.001	<0.01	<0.01	21.45	0.05	<0.001	0.13	0.67
631486	Drill Core	1.22	0.001	0.003	0.39	<0.01	<2	0.004	<0.001	0.03	2.31	<0.02	0.01	<0.001	<0.01	<0.01	21.75	0.05	0.001	0.12	0.59
631487	Drill Core	0.58	0.002	0.003	0.11	0.60	<2	0.006	<0.001	0.03	1.23	<0.02	0.01	0.002	<0.01	<0.01	18.31	0.07	<0.001	0.09	0.49
631488	Drill Core	1.46	<0.001	0.004	0.42	0.41	<2	0.003	<0.001	0.06	2.70	<0.02	0.01	0.001	<0.01	<0.01	25.98	0.09	<0.001	0.11	0.20
631489	Drill Core	1.65	0.005	0.019	0.09	0.29	<2	0.009	<0.001	0.03	1.41	<0.02	0.01	0.001	<0.01	<0.01	21.31	0.85	0.003	0.08	0.44
631490	Drill Core	0.29	0.006	0.016	0.10	0.24	<2	0.010	<0.001	0.03	0.49	<0.02	0.02	0.001	<0.01	<0.01	28.00	1.67	0.004	0.07	0.27
631491	Drill Core	0.23	0.006	0.015	0.09	0.22	<2	0.010	<0.001	0.03	0.52	<0.02	0.02	0.001	<0.01	<0.01	27.34	1.79	0.004	0.07	0.26
631492	Drill Core	1.88	0.005	0.017	0.09	0.19	<2	0.009	<0.001	0.03	0.81	<0.02	0.02	<0.001	<0.01	<0.01	33.87	2.99	0.003	0.07	0.19
631493	Drill Core	1.60	0.005	0.014	0.04	0.13	<2	0.008	<0.001	0.04	0.53	<0.02	0.02	<0.001	<0.01	<0.01	33.88	1.38	0.003	0.08	0.21
631494	Drill Core	0.48	0.006	0.019	0.23	0.71	3	0.011	<0.001	0.04	3.54	<0.02	0.02	0.003	<0.01	<0.01	28.22	0.77	0.005	0.11	0.39
631495	Drill Core	2.13	0.003	0.012	0.06	0.07	<2	0.007	<0.001	0.02	1.35	<0.02	0.01	<0.001	<0.01	<0.01	16.21	0.81	0.001	0.09	0.39
631496	Drill Core	2.01	0.003	0.006	0.21	0.16	<2	0.007	<0.001	0.01	1.17	<0.02	<0.01	<0.001	<0.01	<0.01	12.65	0.64	0.002	0.08	0.48
631497	Drill Core	1.88	0.003	0.011	0.06	0.33	<2	0.009	<0.001	0.02	1.84	<0.02	<0.01	0.001	<0.01	<0.01	13.78	0.22	0.002	0.09	0.52
631498	Drill Core	1.45	0.008	0.040	0.24	0.27	2	0.017	<0.001	0.01	11.93	<0.02	<0.01	<0.001	<0.01	<0.01	6.81	0.26	0.005	0.13	1.01
631499	Drill Core	1.94	0.008	0.015	0.12	1.18	<2	0.017	<0.001	<0.01	1.62	<0.02	<0.01	0.004	<0.01	<0.01	2.67	0.16	0.004	0.15	1.08
631500	Rock	0.43	<0.001	<0.001	<0.02	<0.01	<2	0.001	<0.001	0.01	0.19	<0.02	0.01	<0.001	<0.01	<0.01	21.74	0.03	0.001	10.93	0.15
631501	Drill Core	1.49	0.013	0.019	0.06	0.64	<2	0.027	<0.001	<0.01	0.98	<0.02	<0.01	0.002	<0.01	<0.01	3.82	1.05	0.009	0.27	2.07
631502	Drill Core	0.81	0.002	0.006	3.11	0.94	15	0.023	<0.001	0.01	1.44	<0.02	0.01	0.003	<0.01	<0.01	10.75	2.92	0.021	0.28	2.58
631503	Drill Core	2.86	<0.001	0.004	0.19	0.03	<2	0.007	<0.001	0.03	3.16	<0.02	0.01	<0.001	<0.01	<0.01	20.44	0.65	0.004	0.42	3.04
631504	Drill Core	2.37	0.001	0.003	0.03	<0.01	<2	0.007	<0.001	0.04	2.04	<0.02	0.02	<0.001	<0.01	<0.01	25.78	0.05	0.003	0.31	2.34
631505	Drill Core	0.59	<0.001	0.003	<0.02	<0.01	<2	0.005	<0.001	0.05	4.48	<0.02	0.02	<0.001	<0.01	<0.01	31.77	0.01	0.002	0.19	1.26
631506	Drill Core	1.49	0.003	0.005	0.02	0.22	<2	0.012	<0.001	0.02	3.29	<0.02	0.02	0.001	<0.01	<0.01	20.05	4.38	0.006	0.24	2.16
631507	Drill Core	1.83	0.012	0.014	0.03	0.03	<2	0.035	0.001	<0.01	3.35	<0.02	<0.01	<0.001	<0.01	<0.01	2.74	0.88	0.017	0.48	4.38



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: November 30, 2010

Page: 3 of 3 **Part** 2

CERTIFICATE OF ANALYSIS

WHI10000650.1

	Method Analyte Unit MDL	7TD	7TD	7TD	7TD	7TD.1	G8SG
		Na	K	W	S	Pb	SG
		%	%	%	%	%	
		0.01	0.01	0.01	0.05	0.02	0
631481	Drill Core	<0.01	0.29	<0.01	3.27		2.59
631482	Drill Core	<0.01	0.68	<0.01	5.49		2.56
631483	Drill Core	<0.01	0.32	<0.01	4.92		2.68
631484	Drill Core	<0.01	0.25	<0.01	2.64		2.55
631485	Drill Core	<0.01	0.37	<0.01	1.89		2.47
631486	Drill Core	<0.01	0.29	<0.01	2.78		2.51
631487	Drill Core	<0.01	0.25	<0.01	1.68		2.43
631488	Drill Core	<0.01	0.10	<0.01	3.50		2.59
631489	Drill Core	<0.01	0.23	<0.01	1.80		2.40
631490	Drill Core	<0.01	0.13	<0.01	0.84		2.14
631491	Drill Core	<0.01	0.13	<0.01	0.81		2.32
631492	Drill Core	<0.01	0.09	<0.01	1.18		2.38
631493	Drill Core	<0.01	0.09	<0.01	0.85		2.31
631494	Drill Core	<0.01	0.18	<0.01	4.52		2.44
631495	Drill Core	<0.01	0.20	<0.01	1.52		2.39
631496	Drill Core	<0.01	0.27	<0.01	1.34		2.39
631497	Drill Core	<0.01	0.30	<0.01	2.19		2.38
631498	Drill Core	<0.01	0.61	<0.01	13.07		2.51
631499	Drill Core	<0.01	0.65	<0.01	2.23		2.20
631500	Rock	<0.01	0.01	<0.01	0.14		2.61
631501	Drill Core	<0.01	1.26	<0.01	1.28		2.03
631502	Drill Core	<0.01	1.65	<0.01	2.45		2.17
631503	Drill Core	<0.01	1.04	<0.01	3.55		2.55
631504	Drill Core	<0.01	0.76	<0.01	2.31		2.46
631505	Drill Core	<0.01	0.78	<0.01	5.15		2.63
631506	Drill Core	<0.01	1.33	<0.01	3.75		2.48
631507	Drill Core	<0.01	3.03	<0.01	3.52		1.98



Acme Analytical Laboratories (Vancouver) Ltd.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: **Selwyn Resources Ltd.**

Suite 700 - 509 Richards Street

Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: November 30, 2010

Page: 1 of 2 Part 1

QUALITY CONTROL REPORT

WHI10000650.1

	Method Analyte Unit MDL	WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD
		Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg	Al
		kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%	%
		0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01	0.01
Pulp Duplicates																					
631459	Drill Core	0.90	<0.001	0.003	>10	8.86	4	0.003	<0.001	0.01	0.65	<0.02	<0.01	0.053	<0.01	<0.01	3.64	0.03	<0.001	0.06	0.69
REP 631459	QC																				
631462	Drill Core	1.86	0.004	0.013	3.34	12.99	5	0.009	<0.001	0.02	6.98	<0.02	<0.01	0.054	<0.01	<0.01	0.41	0.04	0.002	0.08	0.99
REP 631462	QC		0.003	0.012	3.29	12.98	4	0.008	<0.001	0.02	6.90	<0.02	<0.01	0.053	<0.01	<0.01	0.40	0.04	0.002	0.08	0.98
631482	Drill Core	1.98	0.003	0.005	1.23	5.31	<2	0.008	<0.001	0.02	2.45	<0.02	<0.01	0.014	<0.01	<0.01	6.48	0.08	0.001	0.12	1.05
REP 631482	QC		0.003	0.005	1.25	5.21	<2	0.008	<0.001	0.02	2.51	<0.02	<0.01	0.014	<0.01	<0.01	6.37	0.09	0.001	0.12	1.03
Core Reject Duplicates																					
631457	Drill Core	0.85	<0.001	0.001	1.10	1.20	<2	0.001	<0.001	0.07	0.56	<0.02	0.02	0.008	<0.01	<0.01	35.50	0.02	<0.001	0.11	0.15
DUP 631457	QC		<0.001	0.002	1.08	1.18	<2	0.001	<0.001	0.07	0.56	<0.02	0.02	0.008	<0.01	<0.01	35.33	0.02	<0.001	0.11	0.15
631492	Drill Core	1.88	0.005	0.017	0.09	0.19	<2	0.009	<0.001	0.03	0.81	<0.02	0.02	<0.001	<0.01	<0.01	33.87	2.99	0.003	0.07	0.19
DUP 631492	QC		0.005	0.017	0.09	0.20	<2	0.009	<0.001	0.03	0.80	<0.02	0.02	<0.001	<0.01	<0.01	31.66	2.97	0.002	0.07	0.18
Reference Materials																					
STD CCU-1C	Standard																				
STD CZN-3	Standard																				
STD OREAS131A	Standard		<0.001	0.032	1.71	2.91	32	0.003	0.002	0.18	5.96	<0.02	<0.01	0.008	<0.01	<0.01	5.50	0.06	0.003	3.14	4.62
STD OREAS131A	Standard		<0.001	0.032	1.71	2.90	31	0.003	0.002	0.18	5.98	<0.02	<0.01	0.008	<0.01	<0.01	5.46	0.06	0.002	3.15	4.63
STD PTC-1A	Standard																				
STD R4T	Standard		0.065	0.519	1.58	3.50	90	0.355	0.044	0.09	24.90	0.02	0.02	0.020	0.02	<0.01	2.24	0.05	0.020	1.45	3.99
STD R4T	Standard		0.066	0.521	1.60	3.52	89	0.360	0.043	0.10	24.88	<0.02	0.02	0.019	0.02	<0.01	2.24	0.05	0.021	1.45	3.88
STD SARM 71	Standard																				
STD SU-1B	Standard		<0.001	1.171	<0.02	0.03	7	1.954	0.067	0.07	25.81	<0.02	0.03	<0.001	<0.01	<0.01	2.22	0.07	0.032	1.81	4.33
STD SU-1B	Standard		<0.001	1.182	<0.02	0.03	7	1.993	0.068	0.08	26.00	<0.02	0.03	<0.001	<0.01	<0.01	2.27	0.08	0.033	1.85	4.45
STD R4T Expected			0.062	0.502	1.518	3.376	86	0.339	0.039	0.086	24.07	0.0087	0.0185	0.018	0.0138	0.0018	2.166	0.045	0.018	1.384	3.897
STD OREAS131A Expected			0.001	0.0322	1.72	2.83	30.9	0.0027	0.0023	0.1722	5.8166	0.0082	0.0028	0.0081	0.0047	0.001	5.286	0.0536	0.0025	3.1182	4.6057
STD SU-1B Expected			0.0004	1.185	0.0058	0.0235	6.4	1.97	0.0672	0.0703	25.54	0.00025	0.03	0.0003	0.00002	0.0003	2.21	0.06	0.032	1.79	4.39
STD CZN-3 Expected																					
STD CCU-1C Expected																					
STD PTC-1A Expected																					



Acme Analytical Laboratories (Vancouver) Ltd.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: Selwyn Resources Ltd.

Suite 700 - 509 Richards Street

Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: November 30, 2010

Page: 1 of 2 **Part** 2

QUALITY CONTROL REPORT

WHI10000650.1

	Method Analyte Unit MDL	7TD	7TD	7TD	7TD	7TD.1	G8SG
		Na	K	W	S	Pb	SG
		%	%	%	%	%	
		0.01	0.01	0.01	0.05	0.02	0
Pulp Duplicates							
631459	Drill Core	<0.01	0.44	<0.01	6.40	9.64	2.83
REP 631459	QC	9.74					
631462	Drill Core	<0.01	0.66	<0.01	14.43		2.83
REP 631462	QC	<0.01	0.65	<0.01	14.41		
631482	Drill Core	<0.01	0.68	<0.01	5.49		2.56
REP 631482	QC	<0.01	0.70	<0.01	5.39		
Core Reject Duplicates							
631457	Drill Core	<0.01	0.08	<0.01	1.69		2.60
DUP 631457	QC	<0.01	0.08	<0.01	1.67		2.56
631492	Drill Core	<0.01	0.09	<0.01	1.18		2.38
DUP 631492	QC	<0.01	0.09	<0.01	1.17		2.40
Reference Materials							
STD CCU-1C	Standard						0.39
STD CZN-3	Standard						0.11
STD OREAS131A	Standard	0.16	3.60	<0.01	5.07		
STD OREAS131A	Standard	0.15	3.36	<0.01	4.71		
STD PTC-1A	Standard						0.05
STD R4T	Standard	0.96	1.24	<0.01	12.73		
STD R4T	Standard	0.96	1.22	<0.01	11.82		
STD SARM 71	Standard						<0.02
STD SU-1B	Standard	1.76	0.64	<0.01	8.90		
STD SU-1B	Standard	1.80	0.65	<0.01	8.24		
STD R4T Expected		0.9	1.153	0.00016	12.9903		
STD OREAS131A Expected		0.1501	3.1584	0.0005	4.8		
STD SU-1B Expected		1.662	0.6	0.0007	8.76		
STD CZN-3 Expected							0.113
STD CCU-1C Expected							0.34
STD PTC-1A Expected							0.05



Acme Analytical Laboratories (Vancouver) Ltd.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: **Selwyn Resources Ltd.**

Suite 700 - 509 Richards Street

Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: November 30, 2010

Page: 2 of 2 Part 1

QUALITY CONTROL REPORT

WHI10000650.1

		WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD
		Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg
		kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%
		0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01
BLK	Blank		<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	<0.01	<0.01	<0.02	<0.01	<0.001	<0.01	<0.01	<0.01	<0.01	<0.001	<0.01
BLK	Blank		<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	<0.01	<0.01	<0.02	<0.01	<0.001	<0.01	<0.01	<0.01	<0.01	<0.001	<0.01
BLK	Blank																			
Prep Wash																				
G1	Prep Blank		<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	0.08	2.59	<0.02	0.08	<0.001	<0.01	<0.01	2.42	0.08	<0.001	0.62
G1	Prep Blank		<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	0.07	2.39	<0.02	0.08	<0.001	<0.01	<0.01	2.40	0.08	<0.001	0.60



Acme Analytical Laboratories (Vancouver) Ltd.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: **Selwyn Resources Ltd.**

Suite 700 - 509 Richards Street

Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: November 30, 2010

Page: 2 of 2 **Part** 2

QUALITY CONTROL REPORT

WHI10000650.1

		7TD Na %	7TD K %	7TD W %	7TD S %	7TD.1 Pb %	G8SG SG
		0.01	0.01	0.01	0.05	0.02	0
BLK	Blank	<0.01	<0.01	<0.01	<0.05		
BLK	Blank	<0.01	<0.01	<0.01	<0.05		
BLK	Blank					<0.02	
Prep Wash							
G1	Prep Blank	2.84	3.23	<0.01	<0.05		2.61
G1	Prep Blank	2.83	3.12	<0.01	<0.05		2.62



1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**

Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Submitted By: Jason K. Dunning

Receiving Lab: Canada-Whitehorse

Received: November 11, 2010

Report Date: December 01, 2010

Page: 1 of 5

CERTIFICATE OF ANALYSIS

WHI10000649.2

CLIENT JOB INFORMATION

Project: Selwyn Project
Shipment ID:
P.O. Number PO # 1024
Number of Samples: 104

SAMPLE DISPOSAL

STOR-PLP Store After 90 days Invoice for Storage
STOR-RJT Store After 90 days Invoice for Storage

Acme does not accept responsibility for samples left at the laboratory after 90 days without prior written instructions for sample storage or return.

Invoice To: Selwyn Resources Ltd.
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6
Canada

CC:

SAMPLE PREPARATION AND ANALYTICAL PROCEDURES

Method Code	Number of Samples	Code Description	Test Wgt (g)	Report Status	Lab
7TD.1	2	4 Acid digestion ICP-ES analysis	0.1	Completed	VAN
R200-250	101	Crush split and pulverize 250g drill core to 200 mesh			WHI
7TD2	104	4 Acid digestion ICP-ES analysis.	0.5	Completed	VAN
G812	104	Specific Gravity on Pulp		Completed	VAN

ADDITIONAL COMMENTS

Version 2 : Revised reporting decimal places for SG.



This report supersedes all previous preliminary and final reports with this file number dated prior to the date on this certificate. Signature indicates final approval; preliminary reports are unsigned and should be used for reference only.
All results are considered the confidential property of the client. Acme assumes the liabilities for actual cost of analysis only.
** asterisk indicates that an analytical result could not be provided due to unusually high levels of interference from other elements.



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: December 01, 2010

Page: 2 of 5 Part 1

CERTIFICATE OF ANALYSIS

WHI10000649.2

	Method Analyte Unit MDL	7TD.1	WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD
		Pb	Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg
		%	kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%
		0.02	0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01
633151	Drill Core		1.84	<0.001	0.005	0.03	0.08	<2	0.014	<0.001	<0.01	1.80	<0.02	0.01	<0.001	<0.01	<0.01	7.55	2.35	0.012	0.92
633152	Drill Core		1.22	0.001	0.009	0.39	7.04	8	0.012	<0.001	0.02	4.49	<0.02	0.02	0.019	<0.01	<0.01	11.01	0.53	0.005	0.54
633153	Drill Core		0.39	0.001	0.007	0.16	2.13	4	0.013	<0.001	0.02	3.28	<0.02	0.01	0.006	<0.01	<0.01	9.58	1.75	0.007	0.77
633154	Drill Core		1.82	<0.001	0.007	<0.02	0.20	<2	0.013	<0.001	<0.01	1.66	<0.02	<0.01	<0.001	<0.01	<0.01	5.47	1.84	0.009	0.75
633155	Drill Core		2.44	0.002	0.004	<0.02	0.32	<2	0.008	<0.001	<0.01	0.95	<0.02	<0.01	0.001	<0.01	<0.01	1.91	0.20	0.002	0.23
633156	Drill Core		1.51	0.001	0.003	<0.02	0.18	<2	0.006	<0.001	<0.01	0.79	<0.02	<0.01	<0.001	<0.01	<0.01	2.36	0.15	0.001	0.16
633157	Drill Core		1.03	0.005	0.010	1.33	6.86	4	0.010	<0.001	0.01	5.58	<0.02	<0.01	0.027	<0.01	<0.01	1.22	0.07	0.002	0.13
633158	Drill Core		1.26	0.004	0.015	3.59	18.30	8	0.009	<0.001	0.01	11.52	<0.02	<0.01	0.070	<0.01	<0.01	0.34	0.05	0.002	0.08
633159	Drill Core		2.29	<0.001	0.006	6.05	24.36	5	0.002	<0.001	<0.01	2.41	<0.02	<0.01	0.140	<0.01	<0.01	0.70	<0.01	<0.001	0.03
633160	Drill Core		0.70	0.003	0.007	2.27	7.07	3	0.008	<0.001	0.03	6.56	<0.02	<0.01	0.024	<0.01	<0.01	6.12	0.06	0.002	0.08
633161	Drill Core		0.45	0.003	0.006	2.00	5.33	3	0.007	<0.001	0.03	6.33	<0.02	<0.01	0.017	<0.01	<0.01	8.54	0.04	0.001	0.08
633162	Drill Core		1.40	0.005	0.004	1.07	1.35	<2	0.010	<0.001	0.02	2.56	<0.02	<0.01	0.004	<0.01	<0.01	6.33	0.04	0.002	0.10
633163	Drill Core		1.79	0.001	0.007	0.43	4.25	<2	0.004	<0.001	0.06	2.08	<0.02	0.02	0.013	<0.01	<0.01	25.94	0.05	<0.001	0.10
633164	Drill Core		2.07	0.001	0.003	0.78	3.55	<2	0.005	<0.001	0.03	1.65	<0.02	<0.01	0.011	<0.01	<0.01	13.43	0.08	0.001	0.11
633165	Drill Core		1.12	0.001	0.002	0.54	1.33	<2	0.002	<0.001	0.05	1.94	<0.02	0.02	0.004	<0.01	<0.01	28.85	0.03	<0.001	0.08
633166	Drill Core		1.94	0.002	0.003	1.04	4.40	<2	0.004	<0.001	0.04	4.55	<0.02	0.01	0.012	<0.01	<0.01	20.97	0.05	0.001	0.10
633167	Drill Core		2.38	0.001	0.003	1.06	4.13	<2	0.006	<0.001	0.01	1.64	<0.02	<0.01	0.013	<0.01	<0.01	4.11	0.05	<0.001	0.09
633168	Drill Core		1.12	0.001	0.003	0.42	2.86	<2	0.004	<0.001	0.04	2.28	<0.02	0.01	0.008	<0.01	<0.01	25.52	0.03	<0.001	0.09
633169	Drill Core		1.18	0.001	0.003	2.50	6.56	<2	0.004	<0.001	0.02	1.56	<0.02	<0.01	0.018	<0.01	<0.01	7.29	0.05	<0.001	0.06
633170	Rock		0.24	<0.001	<0.001	<0.02	<0.01	<2	0.002	<0.001	0.02	0.21	<0.02	0.01	<0.001	<0.01	<0.01	21.20	0.03	0.002	10.78
633171	Drill Core		1.68	0.002	0.004	0.44	2.85	<2	0.007	<0.001	0.03	2.57	<0.02	<0.01	0.008	<0.01	<0.01	12.63	0.08	0.001	0.10
633172	Drill Core		1.14	<0.001	0.002	3.83	5.42	<2	0.002	<0.001	0.03	2.61	<0.02	0.01	0.025	<0.01	<0.01	17.83	0.03	<0.001	0.07
633173	Drill Core	13.16	2.51	<0.001	0.005	>10	18.85	4	<0.001	<0.001	0.02	0.49	<0.02	<0.01	0.107	<0.01	<0.01	14.97	0.01	<0.001	0.03
633174	Drill Core		1.38	0.001	0.004	0.40	0.74	<2	0.005	<0.001	0.03	1.28	<0.02	0.01	0.002	<0.01	<0.01	18.42	0.07	0.001	0.11
633175	Drill Core		1.21	<0.001	0.002	0.15	0.33	<2	0.002	<0.001	0.04	0.78	<0.02	0.01	0.001	<0.01	<0.01	23.13	0.03	<0.001	0.09
633176	Drill Core		1.24	0.001	0.001	0.56	1.49	<2	0.004	<0.001	0.03	1.18	<0.02	0.01	0.006	<0.01	<0.01	18.86	0.04	0.001	0.10
633177	Drill Core		1.51	0.002	0.005	0.10	0.67	<2	0.009	<0.001	0.02	2.44	<0.02	<0.01	0.001	<0.01	<0.01	10.03	0.06	0.001	0.10
633178	Drill Core		1.33	<0.001	0.002	0.04	0.36	<2	0.004	<0.001	0.04	1.11	<0.02	0.02	<0.001	<0.01	<0.01	26.01	0.03	<0.001	0.07
633179	Drill Core		2.76	<0.001	0.002	0.03	0.17	<2	0.004	<0.001	0.02	0.83	<0.02	0.01	<0.001	<0.01	<0.01	16.39	0.03	<0.001	0.06
633180	Rock Pulp		0.06	<0.001	0.484	1.41	4.28	25	0.001	0.001	0.71	5.20	<0.02	0.01	0.027	<0.01	<0.01	4.07	0.05	0.004	1.46



Acme Analytical Laboratories (Vancouver) Ltd.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client:

Selwyn Resources Ltd.

Suite 700 - 509 Richards Street

Vancouver BC V6B 2Z6 Canada

Project:

Selwyn Project

Report Date:

December 01, 2010

Page:

2 of 5

Part 2

CERTIFICATE OF ANALYSIS

WHI10000649.2

	Method Analyte Unit MDL	7TD	7TD	7TD	7TD	7TD	G8SG
		Al	Na	K	W	S	SG
		%	%	%	%	%	
		0.01	0.01	0.01	0.01	0.05	0
633151	Drill Core	3.52	0.02	2.35	<0.01	1.93	2.31
633152	Drill Core	1.67	<0.01	1.07	<0.01	9.00	2.57
633153	Drill Core	2.71	<0.01	1.58	<0.01	4.75	2.36
633154	Drill Core	3.59	0.01	2.48	<0.01	1.82	2.27
633155	Drill Core	1.54	<0.01	0.91	<0.01	1.16	2.39
633156	Drill Core	1.16	<0.01	0.69	<0.01	0.85	2.39
633157	Drill Core	1.32	<0.01	0.79	<0.01	9.78	2.58
633158	Drill Core	1.00	<0.01	0.60	<0.01	22.45	2.92
633159	Drill Core	0.34	<0.01	0.20	<0.01	15.29	3.07
633160	Drill Core	0.80	<0.01	0.48	<0.01	11.22	2.72
633161	Drill Core	0.68	<0.01	0.40	<0.01	10.39	2.67
633162	Drill Core	1.15	<0.01	0.74	<0.01	3.77	2.36
633163	Drill Core	0.43	<0.01	0.25	<0.01	4.84	2.54
633164	Drill Core	0.77	<0.01	0.44	<0.01	3.87	2.49
633165	Drill Core	0.28	<0.01	0.14	<0.01	3.24	2.55
633166	Drill Core	0.54	<0.01	0.29	<0.01	7.87	2.63
633167	Drill Core	0.74	<0.01	0.42	<0.01	3.98	2.49
633168	Drill Core	0.48	<0.01	0.26	<0.01	4.34	2.52
633169	Drill Core	0.52	<0.01	0.29	<0.01	5.39	2.55
633170	Rock	0.20	0.02	0.03	<0.01	0.16	2.71
633171	Drill Core	0.80	<0.01	0.46	<0.01	4.51	2.45
633172	Drill Core	0.26	<0.01	0.13	<0.01	6.48	2.75
633173	Drill Core	0.07	<0.01	0.03	<0.01	11.71	3.19
633174	Drill Core	0.75	<0.01	0.43	<0.01	2.04	2.51
633175	Drill Core	0.32	<0.01	0.17	<0.01	1.21	2.53
633176	Drill Core	0.62	<0.01	0.36	<0.01	2.32	2.57
633177	Drill Core	0.70	<0.01	0.40	<0.01	3.20	2.50
633178	Drill Core	0.26	<0.01	0.14	<0.01	1.62	2.52
633179	Drill Core	0.33	<0.01	0.18	<0.01	1.17	2.47
633180	Rock Pulp	4.05	0.10	3.34	<0.01	5.12	N.A.



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: December 01, 2010

Page: 3 of 5 Part 1

CERTIFICATE OF ANALYSIS

WHI10000649.2

	Method Analyte Unit MDL	7TD.1	WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD
		Pb	Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg
		%	kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%
		0.02	0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01
633181	Drill Core	11.82	1.88	<0.001	0.004	>10	13.33	4	<0.001	<0.001	0.04	0.48	<0.02	0.01	0.072	<0.01	0.01	20.52	0.01	0.003	0.05
633182	Drill Core		1.27	<0.001	0.002	0.67	1.30	<2	0.003	<0.001	0.04	1.32	<0.02	0.02	0.006	<0.01	<0.01	29.95	0.02	0.001	0.09
633183	Drill Core		3.03	<0.001	0.003	0.04	0.03	<2	0.004	<0.001	0.04	1.52	<0.02	0.02	<0.001	<0.01	<0.01	28.62	0.05	0.001	0.11
633184	Drill Core		2.44	0.003	0.005	0.07	0.13	<2	0.011	<0.001	0.02	1.47	<0.02	<0.01	<0.001	<0.01	<0.01	7.45	0.08	0.004	0.17
633185	Drill Core		1.57	<0.001	0.003	0.47	0.57	<2	0.004	<0.001	0.03	1.31	<0.02	0.01	0.002	<0.01	<0.01	21.07	0.03	<0.001	0.07
633186	Drill Core		1.28	<0.001	0.003	0.13	0.63	<2	0.005	<0.001	<0.01	0.56	<0.02	<0.01	0.002	<0.01	<0.01	2.21	0.03	0.001	0.07
633187	Drill Core		0.86	0.001	0.003	0.43	0.50	<2	0.007	<0.001	<0.01	1.20	<0.02	<0.01	0.001	<0.01	<0.01	2.93	0.04	0.001	0.08
633188	Drill Core		2.52	0.002	0.003	0.84	0.51	<2	0.009	<0.001	0.02	1.14	<0.02	<0.01	0.001	<0.01	<0.01	10.21	0.07	0.002	0.12
633189	Drill Core		1.55	0.001	0.004	<0.02	0.01	<2	0.007	<0.001	0.04	1.34	<0.02	0.01	<0.001	<0.01	<0.01	20.19	0.14	0.003	0.15
633190	Drill Core		0.40	<0.001	0.003	7.05	0.02	11	0.006	<0.001	0.03	1.56	<0.02	<0.01	<0.001	<0.01	<0.01	14.46	0.04	0.003	0.11
633191	Drill Core		0.39	0.001	0.002	0.03	0.02	<2	0.005	<0.001	0.02	1.03	<0.02	<0.01	<0.001	<0.01	<0.01	12.90	0.04	0.002	0.13
633192	Drill Core		0.90	<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	0.03	0.29	<0.02	0.03	<0.001	<0.01	<0.01	33.34	0.07	<0.001	0.08
633193	Drill Core		2.66	<0.001	0.005	<0.02	<0.01	<2	0.010	<0.001	0.01	1.60	<0.02	<0.01	<0.001	<0.01	<0.01	6.15	1.15	0.006	0.50
633194	Drill Core		1.45	<0.001	0.010	<0.02	0.18	<2	0.010	<0.001	0.02	1.74	<0.02	<0.01	<0.001	<0.01	<0.01	8.97	1.01	0.004	0.57
633195	Drill Core		1.84	<0.001	0.009	<0.02	0.11	<2	0.013	<0.001	<0.01	1.56	<0.02	<0.01	<0.001	<0.01	<0.01	6.49	1.80	0.004	0.40
633196	Drill Core		2.22	<0.001	0.010	0.06	0.52	<2	0.015	<0.001	0.01	1.75	<0.02	<0.01	0.001	<0.01	<0.01	6.43	1.51	0.007	0.23
633197	Drill Core		1.70	<0.001	0.005	<0.02	0.27	<2	0.011	<0.001	<0.01	0.86	<0.02	<0.01	<0.001	<0.01	<0.01	5.82	1.69	0.005	0.12
633198	Drill Core		1.75	<0.001	0.004	<0.02	0.28	<2	0.009	<0.001	0.01	0.77	<0.02	<0.01	<0.001	<0.01	<0.01	9.06	1.73	0.004	0.09
633199	Drill Core		1.78	0.001	0.004	<0.02	0.17	<2	0.009	<0.001	0.01	0.86	<0.02	<0.01	<0.001	<0.01	<0.01	5.42	0.78	0.003	0.16
633200	Rock		0.25	<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	0.02	0.13	<0.02	0.01	<0.001	<0.01	<0.01	21.75	0.05	<0.001	11.03
633201	Drill Core		1.80	<0.001	0.001	<0.02	<0.01	<2	0.002	<0.001	0.08	0.63	<0.02	0.02	<0.001	<0.01	<0.01	32.23	0.04	<0.001	0.16
633202	Drill Core		1.18	<0.001	0.001	<0.02	0.06	<2	0.004	<0.001	0.01	0.48	<0.02	<0.01	<0.001	<0.01	<0.01	7.44	0.08	0.002	0.11
633203	Drill Core		1.65	<0.001	0.003	<0.02	0.18	<2	0.005	<0.001	<0.01	0.73	<0.02	<0.01	<0.001	<0.01	<0.01	2.70	0.31	0.002	0.12
633204	Drill Core		1.07	<0.001	0.002	<0.02	<0.01	<2	<0.001	<0.001	0.07	1.46	<0.02	0.02	<0.001	<0.01	<0.01	31.03	0.04	<0.001	0.13
633205	Drill Core		1.56	<0.001	0.003	<0.02	0.16	<2	0.005	<0.001	0.02	0.72	<0.02	<0.01	<0.001	<0.01	<0.01	10.45	0.58	0.003	0.14
633206	Drill Core		1.06	<0.001	0.004	<0.02	0.06	<2	0.005	<0.001	0.01	1.49	<0.02	<0.01	<0.001	<0.01	<0.01	5.61	0.65	0.002	0.10
633207	Drill Core		1.20	0.001	0.022	0.08	0.41	<2	0.008	<0.001	0.01	6.94	<0.02	<0.01	0.002	<0.01	<0.01	3.66	0.08	0.002	0.08
633208	Drill Core		1.01	0.002	0.012	3.77	5.78	3	0.007	<0.001	0.02	8.10	<0.02	<0.01	0.033	<0.01	<0.01	3.69	0.10	0.002	0.06
633209	Drill Core		1.37	0.004	0.006	0.70	3.88	2	0.009	<0.001	0.03	4.68	<0.02	<0.01	0.014	<0.01	<0.01	8.86	0.06	0.002	0.12
633210	Rock Pulp		0.06	0.001	0.824	0.91	1.36	220	0.001	0.002	0.23	2.72	0.02	0.01	0.009	0.04	0.01	1.94	<0.01	0.003	0.12



Acme Analytical Laboratories (Vancouver) Ltd.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: Selwyn Resources Ltd.

Suite 700 - 509 Richards Street

Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: December 01, 2010

Page: 3 of 5 **Part** 2

CERTIFICATE OF ANALYSIS

WHI10000649.2

	Method Analyte Unit MDL	7TD	7TD	7TD	7TD	7TD	G8SG
		Al	Na	K	W	S	SG
		%	%	%	%	%	
		0.01	0.01	0.01	0.01	0.05	0
633181	Drill Core	0.06	<0.01	0.03	<0.01	7.57	3.07
633182	Drill Core	0.39	<0.01	0.21	<0.01	2.60	2.59
633183	Drill Core	0.59	<0.01	0.32	<0.01	2.05	2.61
633184	Drill Core	1.57	<0.01	0.93	<0.01	1.78	2.37
633185	Drill Core	0.36	<0.01	0.20	<0.01	2.05	2.71
633186	Drill Core	0.56	<0.01	0.31	<0.01	0.75	2.46
633187	Drill Core	0.60	<0.01	0.33	<0.01	1.42	2.48
633188	Drill Core	0.84	<0.01	0.47	<0.01	1.62	2.21
633189	Drill Core	0.84	<0.01	0.46	<0.01	1.65	2.32
633190	Drill Core	0.65	<0.01	0.36	<0.01	2.93	2.49
633191	Drill Core	0.84	<0.01	0.46	<0.01	1.15	2.29
633192	Drill Core	0.13	<0.01	0.09	<0.01	0.50	2.51
633193	Drill Core	2.24	<0.01	1.39	<0.01	1.58	2.14
633194	Drill Core	2.47	<0.01	1.60	<0.01	1.86	2.12
633195	Drill Core	2.15	0.01	1.39	<0.01	1.63	2.17
633196	Drill Core	1.96	<0.01	1.24	<0.01	2.16	2.10
633197	Drill Core	1.19	<0.01	0.77	<0.01	0.93	2.19
633198	Drill Core	1.03	<0.01	0.69	<0.01	0.89	2.21
633199	Drill Core	1.30	<0.01	0.80	<0.01	0.84	2.23
633200	Rock	0.12	<0.01	0.03	<0.01	0.18	2.63
633201	Drill Core	0.24	0.01	0.13	<0.01	0.98	2.39
633202	Drill Core	0.67	<0.01	0.39	<0.01	0.44	2.34
633203	Drill Core	0.85	<0.01	0.50	<0.01	0.68	2.30
633204	Drill Core	0.21	0.01	0.11	<0.01	1.98	2.49
633205	Drill Core	0.97	<0.01	0.58	<0.01	0.80	2.32
633206	Drill Core	0.92	<0.01	0.59	<0.01	1.64	2.28
633207	Drill Core	0.76	<0.01	0.47	<0.01	8.06	2.43
633208	Drill Core	0.59	<0.01	0.37	<0.01	12.23	2.80
633209	Drill Core	1.52	<0.01	1.11	<0.01	7.44	2.50
633210	Rock Pulp	1.25	0.57	0.29	<0.01	2.11	N.A.



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: December 01, 2010

Page: 4 of 5 Part 1

CERTIFICATE OF ANALYSIS

WHI10000649.2

	Method Analyte Unit MDL	7TD.1	WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD
		Pb	Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg
		%	kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%
		0.02	0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01
633211	Drill Core		1.74	<0.001	0.005	3.40	14.08	3	0.003	<0.001	<0.01	5.30	<0.02	<0.01	0.078	<0.01	<0.01	0.83	0.01	<0.001	0.03
633212	Drill Core		1.66	0.003	0.006	0.81	4.21	2	0.009	<0.001	0.02	8.10	<0.02	<0.01	0.014	<0.01	<0.01	2.72	0.03	0.002	0.07
633213	Drill Core		1.88	0.003	0.005	1.11	5.66	<2	0.010	<0.001	0.02	4.72	<0.02	<0.01	0.016	<0.01	<0.01	3.15	0.03	0.002	0.07
633214	Drill Core		0.79	<0.001	<0.001	0.14	0.48	<2	<0.001	<0.001	0.16	0.92	<0.02	0.02	0.001	<0.01	<0.01	35.36	0.04	<0.001	0.18
633215	Drill Core		2.64	0.005	0.007	1.77	7.73	2	0.010	<0.001	0.03	5.18	<0.02	<0.01	0.019	<0.01	<0.01	5.75	0.09	0.002	0.10
633216	Drill Core		1.25	<0.001	0.001	0.18	0.81	<2	0.002	<0.001	0.04	0.57	<0.02	<0.01	0.002	<0.01	<0.01	18.50	0.02	<0.001	0.05
633217	Drill Core		2.15	0.002	0.003	0.15	0.97	<2	0.005	<0.001	0.01	1.69	<0.02	<0.01	0.003	<0.01	<0.01	8.57	0.05	<0.001	0.07
633218	Drill Core		1.29	0.004	0.005	0.04	1.37	<2	0.009	<0.001	<0.01	2.27	<0.02	<0.01	0.004	<0.01	<0.01	2.62	0.04	0.001	0.08
633219	Drill Core		2.87	<0.001	<0.001	0.13	0.34	<2	<0.001	<0.001	0.07	0.45	<0.02	0.02	<0.001	<0.01	<0.01	35.47	0.02	<0.001	0.11
633220	Drill Core		0.45	<0.001	0.002	1.22	2.45	<2	0.003	<0.001	0.05	0.93	<0.02	0.01	0.007	<0.01	<0.01	26.36	0.08	<0.001	0.11
633221	Drill Core		0.38	<0.001	0.002	1.56	2.23	<2	0.003	<0.001	0.04	0.87	<0.02	0.01	0.006	<0.01	<0.01	24.41	0.09	<0.001	0.10
633222	Drill Core		1.45	<0.001	0.004	0.51	4.13	3	0.007	<0.001	0.03	2.29	<0.02	<0.01	0.011	<0.01	<0.01	12.18	0.11	0.002	0.11
633223	Drill Core		1.78	0.001	0.004	2.07	6.84	<2	0.007	<0.001	0.03	2.66	<0.02	<0.01	0.021	<0.01	<0.01	10.89	0.13	0.001	0.12
633224	Drill Core		2.21	0.001	0.004	1.23	4.94	<2	0.007	<0.001	0.03	3.34	<0.02	<0.01	0.013	<0.01	<0.01	7.33	0.08	0.001	0.10
633225	Drill Core		2.15	0.002	0.003	1.97	6.35	<2	0.004	<0.001	0.04	2.44	<0.02	0.01	0.017	<0.01	<0.01	23.09	0.04	0.001	0.09
633226	Drill Core		1.29	<0.001	0.002	0.32	2.18	<2	0.005	<0.001	0.02	1.46	<0.02	<0.01	0.005	<0.01	<0.01	6.72	0.04	<0.001	0.06
633227	Drill Core		1.22	0.004	0.007	2.28	11.79	3	0.010	<0.001	0.02	5.95	<0.02	<0.01	0.025	<0.01	<0.01	6.84	0.06	0.002	0.09
633228	Drill Core		1.70	0.003	0.005	2.52	8.18	<2	0.008	<0.001	0.02	1.66	<0.02	<0.01	0.018	<0.01	<0.01	6.55	0.09	0.001	0.10
633229	Drill Core		1.67	<0.001	0.001	0.34	0.10	<2	0.004	<0.001	0.02	0.72	<0.02	<0.01	<0.001	<0.01	<0.01	11.77	0.04	<0.001	0.08
633230	Rock		0.32	<0.001	<0.001	<0.02	0.01	<2	<0.001	<0.001	0.02	0.28	<0.02	0.01	<0.001	<0.01	<0.01	20.81	0.04	<0.001	10.92
633231	Drill Core		2.32	0.001	0.001	0.05	0.04	<2	0.003	<0.001	0.04	0.36	<0.02	0.02	<0.001	<0.01	<0.01	27.54	0.05	<0.001	0.12
633232	Drill Core		1.88	0.001	0.002	<0.02	0.09	<2	0.003	<0.001	0.04	0.63	<0.02	0.02	<0.001	<0.01	<0.01	32.51	0.04	<0.001	0.11
633233	Drill Core		1.40	0.003	0.011	0.07	<0.01	<2	0.013	<0.001	0.02	5.79	<0.02	<0.01	<0.001	<0.01	<0.01	8.08	0.08	0.002	0.14
633234	Drill Core		1.06	0.003	0.006	0.03	0.02	<2	0.008	<0.001	0.01	0.78	<0.02	<0.01	<0.001	<0.01	<0.01	7.33	0.06	0.002	0.13
633235	Drill Core		1.20	0.001	0.004	0.03	0.03	<2	0.005	<0.001	0.04	1.64	<0.02	<0.01	<0.001	<0.01	<0.01	13.77	0.04	<0.001	0.10
633236	Drill Core		1.15	0.003	0.005	0.26	1.69	<2	0.009	<0.001	0.01	2.10	<0.02	<0.01	0.004	<0.01	<0.01	3.65	0.43	0.001	0.11
633237	Drill Core		0.97	0.001	0.004	0.14	1.17	<2	0.005	<0.001	0.10	1.66	<0.02	0.02	0.003	<0.01	<0.01	27.12	0.13	<0.001	0.11
633238	Drill Core		1.26	0.002	0.006	0.14	2.11	<2	0.006	<0.001	<0.01	1.48	<0.02	<0.01	0.004	<0.01	<0.01	2.70	0.20	0.001	0.06
633239	Drill Core		0.95	<0.001	0.002	0.10	0.08	<2	0.004	<0.001	0.05	0.21	<0.02	0.02	<0.001	<0.01	<0.01	32.73	0.07	<0.001	0.09
633240	Rock Pulp		0.06	<0.001	0.491	1.42	4.40	28	0.001	0.001	0.68	5.28	<0.02	0.01	0.027	<0.01	<0.01	4.24	0.05	0.003	1.51



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: December 01, 2010

Page: 4 of 5 **Part** 2

CERTIFICATE OF ANALYSIS

WHI10000649.2

	Method Analyte Unit MDL	7TD	7TD	7TD	7TD	7TD	G8SG
		Al	Na	K	W	S	SG
		%	%	%	%	%	
		0.01	0.01	0.01	0.01	0.05	0
633211	Drill Core	0.33	<0.01	0.19	<0.01	12.56	2.97
633212	Drill Core	0.85	<0.01	0.53	<0.01	11.19	2.66
633213	Drill Core	0.96	<0.01	0.61	<0.01	8.51	2.50
633214	Drill Core	0.08	0.01	0.04	<0.01	1.76	2.56
633215	Drill Core	1.24	<0.01	0.80	<0.01	10.30	2.54
633216	Drill Core	0.20	<0.01	0.11	<0.01	1.15	2.51
633217	Drill Core	0.61	<0.01	0.35	<0.01	2.43	2.47
633218	Drill Core	1.07	<0.01	0.65	<0.01	3.12	2.40
633219	Drill Core	0.07	<0.01	0.03	<0.01	1.00	2.52
633220	Drill Core	0.41	<0.01	0.22	<0.01	2.72	2.57
633221	Drill Core	0.39	<0.01	0.21	<0.01	2.55	2.60
633222	Drill Core	0.88	<0.01	0.51	<0.01	5.02	2.47
633223	Drill Core	1.04	<0.01	0.60	<0.01	7.09	2.58
633224	Drill Core	0.89	<0.01	0.54	<0.01	6.72	2.51
633225	Drill Core	0.42	<0.01	0.23	<0.01	6.55	2.62
633226	Drill Core	0.50	<0.01	0.29	<0.01	2.74	2.46
633227	Drill Core	0.81	<0.01	0.49	<0.01	13.22	2.54
633228	Drill Core	0.91	<0.01	0.54	<0.01	6.44	2.35
633229	Drill Core	0.58	<0.01	0.33	<0.01	0.90	2.32
633230	Rock	0.35	0.06	0.08	<0.01	0.21	2.55
633231	Drill Core	0.58	<0.01	0.31	<0.01	0.57	2.38
633232	Drill Core	0.46	<0.01	0.25	<0.01	0.98	2.34
633233	Drill Core	1.35	<0.01	0.82	<0.01	7.26	2.24
633234	Drill Core	1.37	<0.01	0.87	<0.01	0.91	2.13
633235	Drill Core	0.51	<0.01	0.30	<0.01	1.91	2.32
633236	Drill Core	1.01	<0.01	0.61	<0.01	3.22	2.17
633237	Drill Core	0.23	<0.01	0.13	<0.01	2.85	2.38
633238	Drill Core	0.49	<0.01	0.29	<0.01	2.59	2.15
633239	Drill Core	0.31	<0.01	0.17	<0.01	0.52	2.23
633240	Rock Pulp	4.52	0.09	3.28	<0.01	5.41	N.A.



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: December 01, 2010

Page: 5 of 5 Part 1

CERTIFICATE OF ANALYSIS

WHI10000649.2

	Method Analyte Unit MDL	7TD.1	WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD
		Pb	Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	
		%	kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%
		0.02	0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01
633241	Drill Core		1.86	0.006	0.017	0.43	2.73	4	0.010	<0.001	0.02	1.93	<0.02	0.02	0.007	<0.01	<0.01	16.04	3.67	0.004	0.08
633242	Drill Core		1.13	<0.001	0.011	0.21	1.51	2	0.004	<0.001	0.04	6.10	<0.02	0.02	0.004	<0.01	<0.01	25.23	0.02	<0.001	0.10
633243	Drill Core		1.45	0.004	0.009	0.25	1.43	<2	0.010	<0.001	0.02	1.29	<0.02	0.01	0.003	<0.01	<0.01	12.19	0.64	0.002	0.10
633244	Drill Core		1.02	0.002	0.004	0.10	0.12	<2	0.005	<0.001	0.02	0.38	<0.02	0.01	<0.001	<0.01	<0.01	17.34	0.28	0.001	0.07
633245	Drill Core		1.77	0.005	0.011	0.16	1.37	<2	0.010	<0.001	0.02	0.93	<0.02	0.01	0.003	<0.01	<0.01	12.61	0.25	0.003	0.10
633246	Drill Core		2.21	0.007	0.019	0.45	0.93	3	0.015	<0.001	0.01	6.85	<0.02	<0.01	0.002	<0.01	<0.01	9.13	0.23	0.004	0.12
633247	Drill Core		0.98	0.009	0.009	0.03	1.03	<2	0.037	<0.001	<0.01	1.20	<0.02	<0.01	0.003	<0.01	<0.01	3.14	0.37	0.007	0.13
633248	Drill Core		1.82	<0.001	0.002	<0.02	<0.01	<2	0.003	<0.001	0.04	1.87	<0.02	0.02	<0.001	<0.01	<0.01	22.82	0.05	0.003	0.35
633249	Drill Core		2.72	<0.001	0.002	<0.02	<0.01	<2	0.002	<0.001	0.04	1.41	<0.02	0.03	<0.001	<0.01	<0.01	29.12	0.03	0.002	0.35
633250	Drill Core		0.20	0.001	0.005	0.08	0.06	2	0.012	<0.001	0.02	3.23	<0.02	0.01	<0.001	<0.01	<0.01	13.91	0.39	0.009	0.39
633251	Drill Core		0.28	0.001	0.005	0.07	0.03	<2	0.015	<0.001	0.02	3.27	<0.02	0.01	<0.001	<0.01	<0.01	13.87	0.49	0.006	0.34
633252	Drill Core		2.28	<0.001	0.002	<0.02	<0.01	<2	0.002	<0.001	0.04	1.69	<0.02	0.02	<0.001	<0.01	<0.01	24.57	0.04	0.002	0.34
633253	Drill Core		2.26	0.001	0.003	<0.02	<0.01	<2	0.007	<0.001	0.04	1.57	<0.02	0.02	<0.001	<0.01	<0.01	22.25	0.03	0.003	0.38
633254	Drill Core		1.28	0.006	0.008	<0.02	0.14	<2	0.017	<0.001	0.01	3.95	<0.02	0.02	<0.001	<0.01	<0.01	14.63	4.11	0.010	0.29



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**

Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: December 01, 2010

Page: 5 of 5 **Part** 2

CERTIFICATE OF ANALYSIS

WHI10000649.2

	Method Analyte Unit MDL	7TD	7TD	7TD	7TD	7TD	G8SG
		Al	Na	K	W	S	SG
		%	%	%	%	%	
		0.01	0.01	0.01	0.01	0.05	0
633241	Drill Core	0.59	<0.01	0.34	<0.01	3.80	2.18
633242	Drill Core	0.14	<0.01	0.09	<0.01	8.70	2.61
633243	Drill Core	0.73	<0.01	0.42	<0.01	2.29	2.12
633244	Drill Core	0.35	<0.01	0.20	<0.01	0.49	2.23
633245	Drill Core	0.74	<0.01	0.43	<0.01	1.77	2.13
633246	Drill Core	1.03	<0.01	0.60	<0.01	8.96	2.10
633247	Drill Core	1.24	<0.01	0.75	<0.01	1.92	1.67
633248	Drill Core	2.70	<0.01	1.47	<0.01	2.25	2.51
633249	Drill Core	2.20	<0.01	1.21	<0.01	1.73	2.52
633250	Drill Core	3.75	<0.01	1.99	<0.01	3.89	2.21
633251	Drill Core	3.23	<0.01	1.69	<0.01	4.00	2.12
633252	Drill Core	2.36	<0.01	1.29	<0.01	2.03	2.49
633253	Drill Core	3.10	<0.01	1.63	<0.01	1.83	2.28
633254	Drill Core	2.93	<0.01	1.74	<0.01	4.80	2.14



Acme Analytical Laboratories (Vancouver) Ltd.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: **Selwyn Resources Ltd.**

Suite 700 - 509 Richards Street

Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: December 01, 2010

Page: 1 of 2 Part 1

QUALITY CONTROL REPORT

WHI10000649.2

	Method Analyte Unit MDL	7TD.1	WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD
		Pb	Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg
		%	kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%
		0.02	0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01
Pulp Duplicates																					
633173	Drill Core	13.16	2.51	<0.001	0.005	>10	18.85	4	<0.001	<0.001	0.02	0.49	<0.02	<0.01	0.107	<0.01	<0.01	14.97	0.01	<0.001	0.03
REP 633173	QC	13.02																			
633181	Drill Core	11.82	1.88	<0.001	0.004	>10	13.33	4	<0.001	<0.001	0.04	0.48	<0.02	0.01	0.072	<0.01	0.01	20.52	0.01	0.003	0.05
REP 633181	QC	11.91																			
633193	Drill Core		2.66	<0.001	0.005	<0.02	<0.01	<2	0.010	<0.001	0.01	1.60	<0.02	<0.01	<0.001	<0.01	<0.01	6.15	1.15	0.006	0.50
REP 633193	QC			<0.001	0.005	<0.02	<0.01	<2	0.010	<0.001	0.01	1.58	<0.02	<0.01	<0.001	<0.01	<0.01	6.11	1.14	0.006	0.49
633238	Drill Core		1.26	0.002	0.006	0.14	2.11	<2	0.006	<0.001	<0.01	1.48	<0.02	<0.01	0.004	<0.01	<0.01	2.70	0.20	0.001	0.06
REP 633238	QC			0.002	0.005	0.15	2.13	<2	0.006	<0.001	<0.01	1.48	<0.02	<0.01	0.004	<0.01	<0.01	2.75	0.21	<0.001	0.06
Core Reject Duplicates																					
633172	Drill Core		1.14	<0.001	0.002	3.83	5.42	<2	0.002	<0.001	0.03	2.61	<0.02	0.01	0.025	<0.01	<0.01	17.83	0.03	<0.001	0.07
DUP 633172	QC			<0.001	0.002	3.73	5.21	<2	0.002	<0.001	0.03	2.50	<0.02	0.01	0.024	<0.01	<0.01	17.79	0.03	<0.001	0.06
633207	Drill Core		1.20	0.001	0.022	0.08	0.41	<2	0.008	<0.001	0.01	6.94	<0.02	<0.01	0.002	<0.01	<0.01	3.66	0.08	0.002	0.08
DUP 633207	QC			0.001	0.021	0.08	0.43	<2	0.008	<0.001	0.01	6.43	<0.02	<0.01	0.002	<0.01	<0.01	3.71	0.09	0.001	0.09
633242	Drill Core		1.13	<0.001	0.011	0.21	1.51	2	0.004	<0.001	0.04	6.10	<0.02	0.02	0.004	<0.01	<0.01	25.23	0.02	<0.001	0.10
DUP 633242	QC			<0.001	0.011	0.21	1.41	<2	0.004	<0.001	0.04	5.93	<0.02	0.02	0.004	<0.01	<0.01	25.84	0.03	<0.001	0.10
Reference Materials																					
STD CCU-1C	Standard	0.39																			
STD CCU-1C	Standard	0.40																			
STD CZN-3	Standard	0.08																			
STD CZN-3	Standard	0.09																			
STD OREAS131A	Standard			<0.001	0.033	1.72	2.90	32	0.003	0.002	0.17	5.96	<0.02	<0.01	0.008	<0.01	<0.01	5.47	0.06	0.002	3.11
STD OREAS131A	Standard			<0.001	0.032	1.69	2.91	31	0.003	0.002	0.18	5.87	<0.02	<0.01	0.008	<0.01	<0.01	5.41	0.06	0.003	3.11
STD OREAS131A	Standard			<0.001	0.032	1.69	2.91	31	0.003	0.002	0.17	5.84	<0.02	<0.01	0.008	<0.01	<0.01	5.40	0.06	0.002	3.09
STD OREAS131A	Standard			<0.001	0.032	1.64	2.80	31	0.002	0.002	0.17	5.81	<0.02	<0.01	0.008	<0.01	<0.01	5.32	0.05	0.003	3.02
STD PTC-1A	Standard	0.06																			
STD PTC-1A	Standard	0.05																			
STD R4T	Standard			0.065	0.528	1.62	3.56	91	0.359	0.044	0.09	24.86	<0.02	0.02	0.020	0.02	<0.01	2.23	0.05	0.020	1.45
STD R4T	Standard			0.064	0.512	1.53	3.45	88	0.351	0.041	0.09	24.44	<0.02	0.02	0.019	0.02	<0.01	2.20	0.05	0.020	1.40



Acme Analytical Laboratories (Vancouver) Ltd.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: Selwyn Resources Ltd.

Suite 700 - 509 Richards Street

Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: December 01, 2010

Page: 1 of 2 **Part** 2

QUALITY CONTROL REPORT

WHI10000649.2

Method		7TD	7TD	7TD	7TD	7TD	G8SG
Analyte		Al	Na	K	W	S	SG
Unit		%	%	%	%	%	
MDL		0.01	0.01	0.01	0.01	0.05	0
Pulp Duplicates							
633173	Drill Core	0.07	<0.01	0.03	<0.01	11.71	3.19
REP 633173	QC						
633181	Drill Core	0.06	<0.01	0.03	<0.01	7.57	3.07
REP 633181	QC						
633193	Drill Core	2.24	<0.01	1.39	<0.01	1.58	2.14
REP 633193	QC	2.23	<0.01	1.39	<0.01	1.56	
633238	Drill Core	0.49	<0.01	0.29	<0.01	2.59	2.15
REP 633238	QC	0.50	<0.01	0.29	<0.01	2.61	
Core Reject Duplicates							
633172	Drill Core	0.26	<0.01	0.13	<0.01	6.48	2.75
DUP 633172	QC	0.25	<0.01	0.13	<0.01	6.25	2.74
633207	Drill Core	0.76	<0.01	0.47	<0.01	8.06	2.43
DUP 633207	QC	0.78	<0.01	0.48	<0.01	7.51	2.45
633242	Drill Core	0.14	<0.01	0.09	<0.01	8.70	2.61
DUP 633242	QC	0.14	<0.01	0.11	<0.01	8.42	2.61
Reference Materials							
STD CCU-1C	Standard						
STD CCU-1C	Standard						
STD CZN-3	Standard						
STD CZN-3	Standard						
STD OREAS131A	Standard	4.61	0.15	3.46	<0.01	4.98	
STD OREAS131A	Standard	4.60	0.16	3.37	<0.01	4.94	
STD OREAS131A	Standard	4.57	0.15	3.31	<0.01	5.02	
STD OREAS131A	Standard	4.46	0.15	3.35	<0.01	4.72	
STD PTC-1A	Standard						
STD PTC-1A	Standard						
STD R4T	Standard	4.00	0.96	1.24	<0.01	13.55	
STD R4T	Standard	3.91	0.94	1.19	<0.01	11.78	



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: December 01, 2010

Page: 2 of 2 Part 1

QUALITY CONTROL REPORT

WHI10000649.2

		7TD.1 Pb %	WGHT Wgt kg	7TD Mo %	7TD Cu %	7TD Pb %	7TD Zn %	7TD Ag gm/t	7TD Ni %	7TD Co %	7TD Mn %	7TD Fe %	7TD As %	7TD Sr %	7TD Cd %	7TD Sb %	7TD Bi %	7TD Ca %	7TD P %	7TD Cr %	7TD Mg %
		0.02	0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.01	0.01
STD R4T	Standard			0.062	0.512	1.53	3.47	88	0.350	0.040	0.09	24.50	<0.02	0.02	0.018	<0.01	<0.01	2.19	0.05	0.019	1.39
STD R4T	Standard			0.066	0.530	1.58	3.57	90	0.359	0.044	0.10	25.00	<0.02	0.02	0.020	0.02	<0.01	2.29	0.06	0.018	1.45
STD SARM 71	Standard	<0.02																			
STD SARM 71	Standard	<0.02																			
STD SU-1B	Standard			<0.001	1.213	<0.02	0.03	7	2.006	0.069	0.07	26.03	<0.02	0.03	<0.001	<0.01	<0.01	2.25	0.08	0.032	1.83
STD SU-1B	Standard			<0.001	1.152	<0.02	0.03	7	1.921	0.065	0.07	25.41	<0.02	0.03	<0.001	<0.01	<0.01	2.26	0.07	0.031	1.79
STD SU-1B	Standard			<0.001	1.191	<0.02	0.03	7	1.997	0.067	0.07	25.77	<0.02	0.03	<0.001	<0.01	<0.01	2.22	0.08	0.031	1.77
STD SU-1B	Standard			<0.001	1.184	<0.02	0.03	7	1.979	0.068	0.07	25.71	<0.02	0.03	<0.001	<0.01	<0.01	2.28	0.07	0.030	1.80
STD R4T Expected				0.062	0.502	1.518	3.376	86	0.339	0.039	0.086	24.07	0.0087	0.0185	0.018	0.0138	0.0018	2.166	0.045	0.018	1.384
STD OREAS131A Expected				0.001	0.0322	1.72	2.83	30.9	0.0027	0.0023	0.1722	5.8166	0.0082	0.0028	0.0081	0.0047	0.001	5.286	0.0536	0.0025	3.1182
STD SU-1B Expected				0.0004	1.185	0.0058	0.0235	6.4	1.97	0.0672	0.0703	25.54	0.00025	0.03	0.0003	0.00002	0.0003	2.21	0.06	0.032	1.79
STD CZN-3 Expected		0.113																			
STD CCU-1C Expected		0.34																			
STD PTC-1A Expected		0.05																			
BLK	Blank			<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	<0.01	<0.01	<0.02	<0.01	<0.001	<0.01	<0.01	<0.01	<0.01	<0.001	<0.01
BLK	Blank			<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	<0.01	<0.01	<0.02	<0.01	<0.001	<0.01	<0.01	<0.01	<0.01	<0.001	<0.01
BLK	Blank			<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	<0.01	<0.01	<0.02	<0.01	<0.001	<0.01	<0.01	<0.01	<0.01	<0.001	<0.01
BLK	Blank			<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	<0.01	<0.01	<0.02	<0.01	<0.001	<0.01	<0.01	<0.01	<0.01	<0.001	<0.01
BLK	Blank	<0.02																			
BLK	Blank	<0.02																			
Prep Wash																					
G1	Prep Blank			<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	0.07	2.40	<0.02	0.08	<0.001	<0.01	<0.01	2.36	0.08	<0.001	0.61
G1	Prep Blank			<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	0.07	2.43	<0.02	0.08	<0.001	<0.01	<0.01	2.37	0.08	<0.001	0.61



Acme Analytical Laboratories (Vancouver) Ltd.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: **Selwyn Resources Ltd.**

Suite 700 - 509 Richards Street

Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: December 01, 2010

Page: 2 of 2 **Part** 2

QUALITY CONTROL REPORT

WHI10000649.2

		7TD Al %	7TD Na %	7TD K %	7TD W %	7TD S %	G8SG SG
		0.01	0.01	0.01	0.01	0.05	0
STD R4T	Standard	3.84	0.94	1.18	<0.01	12.88	
STD R4T	Standard	4.03	0.97	1.23	<0.01	12.78	
STD SARM 71	Standard						
STD SARM 71	Standard						
STD SU-1B	Standard	4.40	1.79	0.65	<0.01	9.52	
STD SU-1B	Standard	4.37	1.76	0.63	<0.01	8.16	
STD SU-1B	Standard	4.34	1.75	0.62	<0.01	9.28	
STD SU-1B	Standard	4.35	1.72	0.63	<0.01	8.73	
STD R4T Expected		3.897	0.9	1.153	0.00016	12.9903	
STD OREAS131A Expected		4.6057	0.1501	3.1584	0.0005	4.8	
STD SU-1B Expected		4.39	1.662	0.6	0.0007	8.76	
STD CZN-3 Expected							
STD CCU-1C Expected							
STD PTC-1A Expected							
BLK	Blank	<0.01	<0.01	<0.01	<0.01	<0.05	
BLK	Blank	<0.01	<0.01	<0.01	<0.01	<0.05	
BLK	Blank	<0.01	<0.01	<0.01	<0.01	<0.05	
BLK	Blank	<0.01	<0.01	<0.01	<0.01	<0.05	
BLK	Blank						
BLK	Blank						
Prep Wash							
G1	Prep Blank	7.93	2.71	3.06	<0.01	<0.05	2.64
G1	Prep Blank	8.07	2.80	3.02	<0.01	<0.05	2.65



1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: Selwyn Resources Ltd.

Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Submitted By: Jason K. Dunning

Receiving Lab: Canada-Whitehorse

Received: November 11, 2010

Report Date: November 29, 2010

Page: 1 of 5

CERTIFICATE OF ANALYSIS

WHI10000649.1

CLIENT JOB INFORMATION

Project: Selwyn Project
Shipment ID:
P.O. Number PO # 1024
Number of Samples: 104

SAMPLE DISPOSAL

STOR-PLP Store After 90 days Invoice for Storage
STOR-RJT Store After 90 days Invoice for Storage

Acme does not accept responsibility for samples left at the laboratory after 90 days without prior written instructions for sample storage or return.

Invoice To: Selwyn Resources Ltd.
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6
Canada

CC:

SAMPLE PREPARATION AND ANALYTICAL PROCEDURES

Method Code	Number of Samples	Code Description	Test Wgt (g)	Report Status	Lab
7TD.1	2	4 Acid digestion ICP-ES analysis	0.1	Completed	VAN
R200-250	101	Crush split and pulverize 250g drill core to 200 mesh			WHI
7TD2	104	4 Acid digestion ICP-ES analysis.	0.5	Completed	VAN
G812	104	Specific Gravity on Pulp		Completed	VAN

ADDITIONAL COMMENTS



This report supersedes all previous preliminary and final reports with this file number dated prior to the date on this certificate. Signature indicates final approval; preliminary reports are unsigned and should be used for reference only.
All results are considered the confidential property of the client. Acme assumes the liabilities for actual cost of analysis only.
** asterisk indicates that an analytical result could not be provided due to unusually high levels of interference from other elements.



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: November 29, 2010

Page: 2 of 5 Part 1

CERTIFICATE OF ANALYSIS

WHI10000649.1

	Method Analyte Unit MDL	7TD.1	WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD
		Pb	Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg
		%	kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%
		0.02	0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01
633151	Drill Core		1.84	<0.001	0.005	0.03	0.08	<2	0.014	<0.001	<0.01	1.80	<0.02	0.01	<0.001	<0.01	<0.01	7.55	2.35	0.012	0.92
633152	Drill Core		1.22	0.001	0.009	0.39	7.04	8	0.012	<0.001	0.02	4.49	<0.02	0.02	0.019	<0.01	<0.01	11.01	0.53	0.005	0.54
633153	Drill Core		0.39	0.001	0.007	0.16	2.13	4	0.013	<0.001	0.02	3.28	<0.02	0.01	0.006	<0.01	<0.01	9.58	1.75	0.007	0.77
633154	Drill Core		1.82	<0.001	0.007	<0.02	0.20	<2	0.013	<0.001	<0.01	1.66	<0.02	<0.01	<0.001	<0.01	<0.01	5.47	1.84	0.009	0.75
633155	Drill Core		2.44	0.002	0.004	<0.02	0.32	<2	0.008	<0.001	<0.01	0.95	<0.02	<0.01	0.001	<0.01	<0.01	1.91	0.20	0.002	0.23
633156	Drill Core		1.51	0.001	0.003	<0.02	0.18	<2	0.006	<0.001	<0.01	0.79	<0.02	<0.01	<0.001	<0.01	<0.01	2.36	0.15	0.001	0.16
633157	Drill Core		1.03	0.005	0.010	1.33	6.86	4	0.010	<0.001	0.01	5.58	<0.02	<0.01	0.027	<0.01	<0.01	1.22	0.07	0.002	0.13
633158	Drill Core		1.26	0.004	0.015	3.59	18.30	8	0.009	<0.001	0.01	11.52	<0.02	<0.01	0.070	<0.01	<0.01	0.34	0.05	0.002	0.08
633159	Drill Core		2.29	<0.001	0.006	6.05	24.36	5	0.002	<0.001	<0.01	2.41	<0.02	<0.01	0.140	<0.01	<0.01	0.70	<0.01	<0.001	0.03
633160	Drill Core		0.70	0.003	0.007	2.27	7.07	3	0.008	<0.001	0.03	6.56	<0.02	<0.01	0.024	<0.01	<0.01	6.12	0.06	0.002	0.08
633161	Drill Core		0.45	0.003	0.006	2.00	5.33	3	0.007	<0.001	0.03	6.33	<0.02	<0.01	0.017	<0.01	<0.01	8.54	0.04	0.001	0.08
633162	Drill Core		1.40	0.005	0.004	1.07	1.35	<2	0.010	<0.001	0.02	2.56	<0.02	<0.01	0.004	<0.01	<0.01	6.33	0.04	0.002	0.10
633163	Drill Core		1.79	0.001	0.007	0.43	4.25	<2	0.004	<0.001	0.06	2.08	<0.02	0.02	0.013	<0.01	<0.01	25.94	0.05	<0.001	0.10
633164	Drill Core		2.07	0.001	0.003	0.78	3.55	<2	0.005	<0.001	0.03	1.65	<0.02	<0.01	0.011	<0.01	<0.01	13.43	0.08	0.001	0.11
633165	Drill Core		1.12	0.001	0.002	0.54	1.33	<2	0.002	<0.001	0.05	1.94	<0.02	0.02	0.004	<0.01	<0.01	28.85	0.03	<0.001	0.08
633166	Drill Core		1.94	0.002	0.003	1.04	4.40	<2	0.004	<0.001	0.04	4.55	<0.02	0.01	0.012	<0.01	<0.01	20.97	0.05	0.001	0.10
633167	Drill Core		2.38	0.001	0.003	1.06	4.13	<2	0.006	<0.001	0.01	1.64	<0.02	<0.01	0.013	<0.01	<0.01	4.11	0.05	<0.001	0.09
633168	Drill Core		1.12	0.001	0.003	0.42	2.86	<2	0.004	<0.001	0.04	2.28	<0.02	0.01	0.008	<0.01	<0.01	25.52	0.03	<0.001	0.09
633169	Drill Core		1.18	0.001	0.003	2.50	6.56	<2	0.004	<0.001	0.02	1.56	<0.02	<0.01	0.018	<0.01	<0.01	7.29	0.05	<0.001	0.06
633170	Rock		0.24	<0.001	<0.001	<0.02	<0.01	<2	0.002	<0.001	0.02	0.21	<0.02	0.01	<0.001	<0.01	<0.01	21.20	0.03	0.002	10.78
633171	Drill Core		1.68	0.002	0.004	0.44	2.85	<2	0.007	<0.001	0.03	2.57	<0.02	<0.01	0.008	<0.01	<0.01	12.63	0.08	0.001	0.10
633172	Drill Core		1.14	<0.001	0.002	3.83	5.42	<2	0.002	<0.001	0.03	2.61	<0.02	0.01	0.025	<0.01	<0.01	17.83	0.03	<0.001	0.07
633173	Drill Core	13.16	2.51	<0.001	0.005	>10	18.85	4	<0.001	<0.001	0.02	0.49	<0.02	<0.01	0.107	<0.01	<0.01	14.97	0.01	<0.001	0.03
633174	Drill Core		1.38	0.001	0.004	0.40	0.74	<2	0.005	<0.001	0.03	1.28	<0.02	0.01	0.002	<0.01	<0.01	18.42	0.07	0.001	0.11
633175	Drill Core		1.21	<0.001	0.002	0.15	0.33	<2	0.002	<0.001	0.04	0.78	<0.02	0.01	0.001	<0.01	<0.01	23.13	0.03	<0.001	0.09
633176	Drill Core		1.24	0.001	0.001	0.56	1.49	<2	0.004	<0.001	0.03	1.18	<0.02	0.01	0.006	<0.01	<0.01	18.86	0.04	0.001	0.10
633177	Drill Core		1.51	0.002	0.005	0.10	0.67	<2	0.009	<0.001	0.02	2.44	<0.02	<0.01	0.001	<0.01	<0.01	10.03	0.06	0.001	0.10
633178	Drill Core		1.33	<0.001	0.002	0.04	0.36	<2	0.004	<0.001	0.04	1.11	<0.02	0.02	<0.001	<0.01	<0.01	26.01	0.03	<0.001	0.07
633179	Drill Core		2.76	<0.001	0.002	0.03	0.17	<2	0.004	<0.001	0.02	0.83	<0.02	0.01	<0.001	<0.01	<0.01	16.39	0.03	<0.001	0.06
633180	Rock Pulp		0.06	<0.001	0.484	1.41	4.28	25	0.001	0.001	0.71	5.20	<0.02	0.01	0.027	<0.01	<0.01	4.07	0.05	0.004	1.46



Acme Analytical Laboratories (Vancouver) Ltd.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client:

Selwyn Resources Ltd.

Suite 700 - 509 Richards Street

Vancouver BC V6B 2Z6 Canada

Project:

Selwyn Project

Report Date:

November 29, 2010

Page:

2 of 5

Part 2

CERTIFICATE OF ANALYSIS

WHI10000649.1

	Method Analyte Unit MDL	7TD	7TD	7TD	7TD	7TD	G8SG
		Al	Na	K	W	S	SG
		%	%	%	%	%	
		0.01	0.01	0.01	0.01	0.05	0
633151	Drill Core	3.52	0.02	2.35	<0.01	1.93	2.31105
633152	Drill Core	1.67	<0.01	1.07	<0.01	9.00	2.57213
633153	Drill Core	2.71	<0.01	1.58	<0.01	4.75	2.35988
633154	Drill Core	3.59	0.01	2.48	<0.01	1.82	2.26599
633155	Drill Core	1.54	<0.01	0.91	<0.01	1.16	2.39161
633156	Drill Core	1.16	<0.01	0.69	<0.01	0.85	2.39291
633157	Drill Core	1.32	<0.01	0.79	<0.01	9.78	2.57533
633158	Drill Core	1.00	<0.01	0.60	<0.01	22.45	2.92121
633159	Drill Core	0.34	<0.01	0.20	<0.01	15.29	3.06873
633160	Drill Core	0.80	<0.01	0.48	<0.01	11.22	2.71576
633161	Drill Core	0.68	<0.01	0.40	<0.01	10.39	2.67212
633162	Drill Core	1.15	<0.01	0.74	<0.01	3.77	2.36191
633163	Drill Core	0.43	<0.01	0.25	<0.01	4.84	2.53596
633164	Drill Core	0.77	<0.01	0.44	<0.01	3.87	2.4943
633165	Drill Core	0.28	<0.01	0.14	<0.01	3.24	2.54713
633166	Drill Core	0.54	<0.01	0.29	<0.01	7.87	2.62523
633167	Drill Core	0.74	<0.01	0.42	<0.01	3.98	2.4906
633168	Drill Core	0.48	<0.01	0.26	<0.01	4.34	2.51844
633169	Drill Core	0.52	<0.01	0.29	<0.01	5.39	2.54729
633170	Rock	0.20	0.02	0.03	<0.01	0.16	2.7143
633171	Drill Core	0.80	<0.01	0.46	<0.01	4.51	2.45402
633172	Drill Core	0.26	<0.01	0.13	<0.01	6.48	2.74618
633173	Drill Core	0.07	<0.01	0.03	<0.01	11.71	3.19444
633174	Drill Core	0.75	<0.01	0.43	<0.01	2.04	2.50994
633175	Drill Core	0.32	<0.01	0.17	<0.01	1.21	2.53175
633176	Drill Core	0.62	<0.01	0.36	<0.01	2.32	2.56953
633177	Drill Core	0.70	<0.01	0.40	<0.01	3.20	2.5024
633178	Drill Core	0.26	<0.01	0.14	<0.01	1.62	2.51772
633179	Drill Core	0.33	<0.01	0.18	<0.01	1.17	2.4731
633180	Rock Pulp	4.05	0.10	3.34	<0.01	5.12	N.A.



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: November 29, 2010

Page: 3 of 5 Part 1

CERTIFICATE OF ANALYSIS

WHI10000649.1

	Method Analyte Unit MDL	7TD.1	WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD
		Pb	Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg
		%	kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%
		0.02	0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01
633181	Drill Core	11.82	1.88	<0.001	0.004	>10	13.33	4	<0.001	<0.001	0.04	0.48	<0.02	0.01	0.072	<0.01	0.01	20.52	0.01	0.003	0.05
633182	Drill Core		1.27	<0.001	0.002	0.67	1.30	<2	0.003	<0.001	0.04	1.32	<0.02	0.02	0.006	<0.01	<0.01	29.95	0.02	0.001	0.09
633183	Drill Core		3.03	<0.001	0.003	0.04	0.03	<2	0.004	<0.001	0.04	1.52	<0.02	0.02	<0.001	<0.01	<0.01	28.62	0.05	0.001	0.11
633184	Drill Core		2.44	0.003	0.005	0.07	0.13	<2	0.011	<0.001	0.02	1.47	<0.02	<0.01	<0.001	<0.01	<0.01	7.45	0.08	0.004	0.17
633185	Drill Core		1.57	<0.001	0.003	0.47	0.57	<2	0.004	<0.001	0.03	1.31	<0.02	0.01	0.002	<0.01	<0.01	21.07	0.03	<0.001	0.07
633186	Drill Core		1.28	<0.001	0.003	0.13	0.63	<2	0.005	<0.001	<0.01	0.56	<0.02	<0.01	0.002	<0.01	<0.01	2.21	0.03	0.001	0.07
633187	Drill Core		0.86	0.001	0.003	0.43	0.50	<2	0.007	<0.001	<0.01	1.20	<0.02	<0.01	0.001	<0.01	<0.01	2.93	0.04	0.001	0.08
633188	Drill Core		2.52	0.002	0.003	0.84	0.51	<2	0.009	<0.001	0.02	1.14	<0.02	<0.01	0.001	<0.01	<0.01	10.21	0.07	0.002	0.12
633189	Drill Core		1.55	0.001	0.004	<0.02	0.01	<2	0.007	<0.001	0.04	1.34	<0.02	0.01	<0.001	<0.01	<0.01	20.19	0.14	0.003	0.15
633190	Drill Core		0.40	<0.001	0.003	7.05	0.02	11	0.006	<0.001	0.03	1.56	<0.02	<0.01	<0.001	<0.01	<0.01	14.46	0.04	0.003	0.11
633191	Drill Core		0.39	0.001	0.002	0.03	0.02	<2	0.005	<0.001	0.02	1.03	<0.02	<0.01	<0.001	<0.01	<0.01	12.90	0.04	0.002	0.13
633192	Drill Core		0.90	<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	0.03	0.29	<0.02	0.03	<0.001	<0.01	<0.01	33.34	0.07	<0.001	0.08
633193	Drill Core		2.66	<0.001	0.005	<0.02	<0.01	<2	0.010	<0.001	0.01	1.60	<0.02	<0.01	<0.001	<0.01	<0.01	6.15	1.15	0.006	0.50
633194	Drill Core		1.45	<0.001	0.010	<0.02	0.18	<2	0.010	<0.001	0.02	1.74	<0.02	<0.01	<0.001	<0.01	<0.01	8.97	1.01	0.004	0.57
633195	Drill Core		1.84	<0.001	0.009	<0.02	0.11	<2	0.013	<0.001	<0.01	1.56	<0.02	<0.01	<0.001	<0.01	<0.01	6.49	1.80	0.004	0.40
633196	Drill Core		2.22	<0.001	0.010	0.06	0.52	<2	0.015	<0.001	0.01	1.75	<0.02	<0.01	0.001	<0.01	<0.01	6.43	1.51	0.007	0.23
633197	Drill Core		1.70	<0.001	0.005	<0.02	0.27	<2	0.011	<0.001	<0.01	0.86	<0.02	<0.01	<0.001	<0.01	<0.01	5.82	1.69	0.005	0.12
633198	Drill Core		1.75	<0.001	0.004	<0.02	0.28	<2	0.009	<0.001	0.01	0.77	<0.02	<0.01	<0.001	<0.01	<0.01	9.06	1.73	0.004	0.09
633199	Drill Core		1.78	0.001	0.004	<0.02	0.17	<2	0.009	<0.001	0.01	0.86	<0.02	<0.01	<0.001	<0.01	<0.01	5.42	0.78	0.003	0.16
633200	Rock		0.25	<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	0.02	0.13	<0.02	0.01	<0.001	<0.01	<0.01	21.75	0.05	<0.001	11.03
633201	Drill Core		1.80	<0.001	0.001	<0.02	<0.01	<2	0.002	<0.001	0.08	0.63	<0.02	0.02	<0.001	<0.01	<0.01	32.23	0.04	<0.001	0.16
633202	Drill Core		1.18	<0.001	0.001	<0.02	0.06	<2	0.004	<0.001	0.01	0.48	<0.02	<0.01	<0.001	<0.01	<0.01	7.44	0.08	0.002	0.11
633203	Drill Core		1.65	<0.001	0.003	<0.02	0.18	<2	0.005	<0.001	<0.01	0.73	<0.02	<0.01	<0.001	<0.01	<0.01	2.70	0.31	0.002	0.12
633204	Drill Core		1.07	<0.001	0.002	<0.02	<0.01	<2	<0.001	<0.001	0.07	1.46	<0.02	0.02	<0.001	<0.01	<0.01	31.03	0.04	<0.001	0.13
633205	Drill Core		1.56	<0.001	0.003	<0.02	0.16	<2	0.005	<0.001	0.02	0.72	<0.02	<0.01	<0.001	<0.01	<0.01	10.45	0.58	0.003	0.14
633206	Drill Core		1.06	<0.001	0.004	<0.02	0.06	<2	0.005	<0.001	0.01	1.49	<0.02	<0.01	<0.001	<0.01	<0.01	5.61	0.65	0.002	0.10
633207	Drill Core		1.20	0.001	0.022	0.08	0.41	<2	0.008	<0.001	0.01	6.94	<0.02	<0.01	0.002	<0.01	<0.01	3.66	0.08	0.002	0.08
633208	Drill Core		1.01	0.002	0.012	3.77	5.78	3	0.007	<0.001	0.02	8.10	<0.02	<0.01	0.033	<0.01	<0.01	3.69	0.10	0.002	0.06
633209	Drill Core		1.37	0.004	0.006	0.70	3.88	2	0.009	<0.001	0.03	4.68	<0.02	<0.01	0.014	<0.01	<0.01	8.86	0.06	0.002	0.12
633210	Rock Pulp		0.06	0.001	0.824	0.91	1.36	220	0.001	0.002	0.23	2.72	0.02	0.01	0.009	0.04	0.01	1.94	<0.01	0.003	0.12



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: November 29, 2010

Page: 3 of 5 **Part** 2

CERTIFICATE OF ANALYSIS

WHI10000649.1

	Method Analyte Unit MDL	7TD	7TD	7TD	7TD	7TD	G8SG
		Al	Na	K	W	S	SG
		%	%	%	%	%	
		0.01	0.01	0.01	0.01	0.05	0
633181	Drill Core	0.06	<0.01	0.03	<0.01	7.57	3.07415
633182	Drill Core	0.39	<0.01	0.21	<0.01	2.60	2.58906
633183	Drill Core	0.59	<0.01	0.32	<0.01	2.05	2.60845
633184	Drill Core	1.57	<0.01	0.93	<0.01	1.78	2.36633
633185	Drill Core	0.36	<0.01	0.20	<0.01	2.05	2.70916
633186	Drill Core	0.56	<0.01	0.31	<0.01	0.75	2.45821
633187	Drill Core	0.60	<0.01	0.33	<0.01	1.42	2.4759
633188	Drill Core	0.84	<0.01	0.47	<0.01	1.62	2.20887
633189	Drill Core	0.84	<0.01	0.46	<0.01	1.65	2.31548
633190	Drill Core	0.65	<0.01	0.36	<0.01	2.93	2.49321
633191	Drill Core	0.84	<0.01	0.46	<0.01	1.15	2.29313
633192	Drill Core	0.13	<0.01	0.09	<0.01	0.50	2.51005
633193	Drill Core	2.24	<0.01	1.39	<0.01	1.58	2.14012
633194	Drill Core	2.47	<0.01	1.60	<0.01	1.86	2.12212
633195	Drill Core	2.15	0.01	1.39	<0.01	1.63	2.16623
633196	Drill Core	1.96	<0.01	1.24	<0.01	2.16	2.10232
633197	Drill Core	1.19	<0.01	0.77	<0.01	0.93	2.18851
633198	Drill Core	1.03	<0.01	0.69	<0.01	0.89	2.21382
633199	Drill Core	1.30	<0.01	0.80	<0.01	0.84	2.22618
633200	Rock	0.12	<0.01	0.03	<0.01	0.18	2.62787
633201	Drill Core	0.24	0.01	0.13	<0.01	0.98	2.3919
633202	Drill Core	0.67	<0.01	0.39	<0.01	0.44	2.33833
633203	Drill Core	0.85	<0.01	0.50	<0.01	0.68	2.29984
633204	Drill Core	0.21	0.01	0.11	<0.01	1.98	2.48859
633205	Drill Core	0.97	<0.01	0.58	<0.01	0.80	2.32005
633206	Drill Core	0.92	<0.01	0.59	<0.01	1.64	2.27642
633207	Drill Core	0.76	<0.01	0.47	<0.01	8.06	2.43191
633208	Drill Core	0.59	<0.01	0.37	<0.01	12.23	2.7955
633209	Drill Core	1.52	<0.01	1.11	<0.01	7.44	2.5009
633210	Rock Pulp	1.25	0.57	0.29	<0.01	2.11	N.A.



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: November 29, 2010

Page: 4 of 5 Part 1

CERTIFICATE OF ANALYSIS

WHI10000649.1

	Method Analyte Unit MDL	7TD.1	WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD
		Pb	Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg
		%	kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%
		0.02	0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01
633211	Drill Core		1.74	<0.001	0.005	3.40	14.08	3	0.003	<0.001	<0.01	5.30	<0.02	<0.01	0.078	<0.01	<0.01	0.83	0.01	<0.001	0.03
633212	Drill Core		1.66	0.003	0.006	0.81	4.21	2	0.009	<0.001	0.02	8.10	<0.02	<0.01	0.014	<0.01	<0.01	2.72	0.03	0.002	0.07
633213	Drill Core		1.88	0.003	0.005	1.11	5.66	<2	0.010	<0.001	0.02	4.72	<0.02	<0.01	0.016	<0.01	<0.01	3.15	0.03	0.002	0.07
633214	Drill Core		0.79	<0.001	<0.001	0.14	0.48	<2	<0.001	<0.001	0.16	0.92	<0.02	0.02	0.001	<0.01	<0.01	35.36	0.04	<0.001	0.18
633215	Drill Core		2.64	0.005	0.007	1.77	7.73	2	0.010	<0.001	0.03	5.18	<0.02	<0.01	0.019	<0.01	<0.01	5.75	0.09	0.002	0.10
633216	Drill Core		1.25	<0.001	0.001	0.18	0.81	<2	0.002	<0.001	0.04	0.57	<0.02	<0.01	0.002	<0.01	<0.01	18.50	0.02	<0.001	0.05
633217	Drill Core		2.15	0.002	0.003	0.15	0.97	<2	0.005	<0.001	0.01	1.69	<0.02	<0.01	0.003	<0.01	<0.01	8.57	0.05	<0.001	0.07
633218	Drill Core		1.29	0.004	0.005	0.04	1.37	<2	0.009	<0.001	<0.01	2.27	<0.02	<0.01	0.004	<0.01	<0.01	2.62	0.04	0.001	0.08
633219	Drill Core		2.87	<0.001	<0.001	0.13	0.34	<2	<0.001	<0.001	0.07	0.45	<0.02	0.02	<0.001	<0.01	<0.01	35.47	0.02	<0.001	0.11
633220	Drill Core		0.45	<0.001	0.002	1.22	2.45	<2	0.003	<0.001	0.05	0.93	<0.02	0.01	0.007	<0.01	<0.01	26.36	0.08	<0.001	0.11
633221	Drill Core		0.38	<0.001	0.002	1.56	2.23	<2	0.003	<0.001	0.04	0.87	<0.02	0.01	0.006	<0.01	<0.01	24.41	0.09	<0.001	0.10
633222	Drill Core		1.45	<0.001	0.004	0.51	4.13	3	0.007	<0.001	0.03	2.29	<0.02	<0.01	0.011	<0.01	<0.01	12.18	0.11	0.002	0.11
633223	Drill Core		1.78	0.001	0.004	2.07	6.84	<2	0.007	<0.001	0.03	2.66	<0.02	<0.01	0.021	<0.01	<0.01	10.89	0.13	0.001	0.12
633224	Drill Core		2.21	0.001	0.004	1.23	4.94	<2	0.007	<0.001	0.03	3.34	<0.02	<0.01	0.013	<0.01	<0.01	7.33	0.08	0.001	0.10
633225	Drill Core		2.15	0.002	0.003	1.97	6.35	<2	0.004	<0.001	0.04	2.44	<0.02	0.01	0.017	<0.01	<0.01	23.09	0.04	0.001	0.09
633226	Drill Core		1.29	<0.001	0.002	0.32	2.18	<2	0.005	<0.001	0.02	1.46	<0.02	<0.01	0.005	<0.01	<0.01	6.72	0.04	<0.001	0.06
633227	Drill Core		1.22	0.004	0.007	2.28	11.79	3	0.010	<0.001	0.02	5.95	<0.02	<0.01	0.025	<0.01	<0.01	6.84	0.06	0.002	0.09
633228	Drill Core		1.70	0.003	0.005	2.52	8.18	<2	0.008	<0.001	0.02	1.66	<0.02	<0.01	0.018	<0.01	<0.01	6.55	0.09	0.001	0.10
633229	Drill Core		1.67	<0.001	0.001	0.34	0.10	<2	0.004	<0.001	0.02	0.72	<0.02	<0.01	<0.001	<0.01	<0.01	11.77	0.04	<0.001	0.08
633230	Rock		0.32	<0.001	<0.001	<0.02	0.01	<2	<0.001	<0.001	0.02	0.28	<0.02	0.01	<0.001	<0.01	<0.01	20.81	0.04	<0.001	10.92
633231	Drill Core		2.32	0.001	0.001	0.05	0.04	<2	0.003	<0.001	0.04	0.36	<0.02	0.02	<0.001	<0.01	<0.01	27.54	0.05	<0.001	0.12
633232	Drill Core		1.88	0.001	0.002	<0.02	0.09	<2	0.003	<0.001	0.04	0.63	<0.02	0.02	<0.001	<0.01	<0.01	32.51	0.04	<0.001	0.11
633233	Drill Core		1.40	0.003	0.011	0.07	<0.01	<2	0.013	<0.001	0.02	5.79	<0.02	<0.01	<0.001	<0.01	<0.01	8.08	0.08	0.002	0.14
633234	Drill Core		1.06	0.003	0.006	0.03	0.02	<2	0.008	<0.001	0.01	0.78	<0.02	<0.01	<0.001	<0.01	<0.01	7.33	0.06	0.002	0.13
633235	Drill Core		1.20	0.001	0.004	0.03	0.03	<2	0.005	<0.001	0.04	1.64	<0.02	<0.01	<0.001	<0.01	<0.01	13.77	0.04	<0.001	0.10
633236	Drill Core		1.15	0.003	0.005	0.26	1.69	<2	0.009	<0.001	0.01	2.10	<0.02	<0.01	0.004	<0.01	<0.01	3.65	0.43	0.001	0.11
633237	Drill Core		0.97	0.001	0.004	0.14	1.17	<2	0.005	<0.001	0.10	1.66	<0.02	0.02	0.003	<0.01	<0.01	27.12	0.13	<0.001	0.11
633238	Drill Core		1.26	0.002	0.006	0.14	2.11	<2	0.006	<0.001	<0.01	1.48	<0.02	<0.01	0.004	<0.01	<0.01	2.70	0.20	0.001	0.06
633239	Drill Core		0.95	<0.001	0.002	0.10	0.08	<2	0.004	<0.001	0.05	0.21	<0.02	0.02	<0.001	<0.01	<0.01	32.73	0.07	<0.001	0.09
633240	Rock Pulp		0.06	<0.001	0.491	1.42	4.40	28	0.001	0.001	0.68	5.28	<0.02	0.01	0.027	<0.01	<0.01	4.24	0.05	0.003	1.51



Acme Analytical Laboratories (Vancouver) Ltd.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client:

Selwyn Resources Ltd.

Suite 700 - 509 Richards Street

Vancouver BC V6B 2Z6 Canada

Project:

Selwyn Project

Report Date:

November 29, 2010

Page:

4 of 5

Part 2

CERTIFICATE OF ANALYSIS

WHI10000649.1

	Method Analyte Unit MDL	7TD	7TD	7TD	7TD	7TD	G8SG
		Al	Na	K	W	S	SG
		%	%	%	%	%	
		0.01	0.01	0.01	0.01	0.05	0
633211	Drill Core	0.33	<0.01	0.19	<0.01	12.56	2.96909
633212	Drill Core	0.85	<0.01	0.53	<0.01	11.19	2.6622
633213	Drill Core	0.96	<0.01	0.61	<0.01	8.51	2.50211
633214	Drill Core	0.08	0.01	0.04	<0.01	1.76	2.55676
633215	Drill Core	1.24	<0.01	0.80	<0.01	10.30	2.53559
633216	Drill Core	0.20	<0.01	0.11	<0.01	1.15	2.51458
633217	Drill Core	0.61	<0.01	0.35	<0.01	2.43	2.47008
633218	Drill Core	1.07	<0.01	0.65	<0.01	3.12	2.3952
633219	Drill Core	0.07	<0.01	0.03	<0.01	1.00	2.52102
633220	Drill Core	0.41	<0.01	0.22	<0.01	2.72	2.56514
633221	Drill Core	0.39	<0.01	0.21	<0.01	2.55	2.59521
633222	Drill Core	0.88	<0.01	0.51	<0.01	5.02	2.47058
633223	Drill Core	1.04	<0.01	0.60	<0.01	7.09	2.58479
633224	Drill Core	0.89	<0.01	0.54	<0.01	6.72	2.50837
633225	Drill Core	0.42	<0.01	0.23	<0.01	6.55	2.61955
633226	Drill Core	0.50	<0.01	0.29	<0.01	2.74	2.46081
633227	Drill Core	0.81	<0.01	0.49	<0.01	13.22	2.53791
633228	Drill Core	0.91	<0.01	0.54	<0.01	6.44	2.34696
633229	Drill Core	0.58	<0.01	0.33	<0.01	0.90	2.31803
633230	Rock	0.35	0.06	0.08	<0.01	0.21	2.54692
633231	Drill Core	0.58	<0.01	0.31	<0.01	0.57	2.38213
633232	Drill Core	0.46	<0.01	0.25	<0.01	0.98	2.3381
633233	Drill Core	1.35	<0.01	0.82	<0.01	7.26	2.23986
633234	Drill Core	1.37	<0.01	0.87	<0.01	0.91	2.12847
633235	Drill Core	0.51	<0.01	0.30	<0.01	1.91	2.31844
633236	Drill Core	1.01	<0.01	0.61	<0.01	3.22	2.16721
633237	Drill Core	0.23	<0.01	0.13	<0.01	2.85	2.37598
633238	Drill Core	0.49	<0.01	0.29	<0.01	2.59	2.15065
633239	Drill Core	0.31	<0.01	0.17	<0.01	0.52	2.22762
633240	Rock Pulp	4.52	0.09	3.28	<0.01	5.41	N.A.



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: Selwyn Resources Ltd.
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: November 29, 2010

Page: 5 of 5 **Part** 1

CERTIFICATE OF ANALYSIS

WHI10000649.1

	Method Analyte Unit MDL	7TD.1	WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD
		Pb	Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg
		%	kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%
		0.02	0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01
633241	Drill Core		1.86	0.006	0.017	0.43	2.73	4	0.010	<0.001	0.02	1.93	<0.02	0.02	0.007	<0.01	<0.01	16.04	3.67	0.004	0.08
633242	Drill Core		1.13	<0.001	0.011	0.21	1.51	2	0.004	<0.001	0.04	6.10	<0.02	0.02	0.004	<0.01	<0.01	25.23	0.02	<0.001	0.10
633243	Drill Core		1.45	0.004	0.009	0.25	1.43	<2	0.010	<0.001	0.02	1.29	<0.02	0.01	0.003	<0.01	<0.01	12.19	0.64	0.002	0.10
633244	Drill Core		1.02	0.002	0.004	0.10	0.12	<2	0.005	<0.001	0.02	0.38	<0.02	0.01	<0.001	<0.01	<0.01	17.34	0.28	0.001	0.07
633245	Drill Core		1.77	0.005	0.011	0.16	1.37	<2	0.010	<0.001	0.02	0.93	<0.02	0.01	0.003	<0.01	<0.01	12.61	0.25	0.003	0.10
633246	Drill Core		2.21	0.007	0.019	0.45	0.93	3	0.015	<0.001	0.01	6.85	<0.02	<0.01	0.002	<0.01	<0.01	9.13	0.23	0.004	0.12
633247	Drill Core		0.98	0.009	0.009	0.03	1.03	<2	0.037	<0.001	<0.01	1.20	<0.02	<0.01	0.003	<0.01	<0.01	3.14	0.37	0.007	0.13
633248	Drill Core		1.82	<0.001	0.002	<0.02	<0.01	<2	0.003	<0.001	0.04	1.87	<0.02	0.02	<0.001	<0.01	<0.01	22.82	0.05	0.003	0.35
633249	Drill Core		2.72	<0.001	0.002	<0.02	<0.01	<2	0.002	<0.001	0.04	1.41	<0.02	0.03	<0.001	<0.01	<0.01	29.12	0.03	0.002	0.35
633250	Drill Core		0.20	0.001	0.005	0.08	0.06	2	0.012	<0.001	0.02	3.23	<0.02	0.01	<0.001	<0.01	<0.01	13.91	0.39	0.009	0.39
633251	Drill Core		0.28	0.001	0.005	0.07	0.03	<2	0.015	<0.001	0.02	3.27	<0.02	0.01	<0.001	<0.01	<0.01	13.87	0.49	0.006	0.34
633252	Drill Core		2.28	<0.001	0.002	<0.02	<0.01	<2	0.002	<0.001	0.04	1.69	<0.02	0.02	<0.001	<0.01	<0.01	24.57	0.04	0.002	0.34
633253	Drill Core		2.26	0.001	0.003	<0.02	<0.01	<2	0.007	<0.001	0.04	1.57	<0.02	0.02	<0.001	<0.01	<0.01	22.25	0.03	0.003	0.38
633254	Drill Core		1.28	0.006	0.008	<0.02	0.14	<2	0.017	<0.001	0.01	3.95	<0.02	0.02	<0.001	<0.01	<0.01	14.63	4.11	0.010	0.29



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: November 29, 2010

Page: 5 of 5 **Part** 2

CERTIFICATE OF ANALYSIS

WHI10000649.1

	Method	7TD	7TD	7TD	7TD	7TD	G8SG
	Analyte	Al	Na	K	W	S	SG
	Unit	%	%	%	%	%	
	MDL	0.01	0.01	0.01	0.01	0.05	0
633241	Drill Core	0.59	<0.01	0.34	<0.01	3.80	2.17971
633242	Drill Core	0.14	<0.01	0.09	<0.01	8.70	2.60616
633243	Drill Core	0.73	<0.01	0.42	<0.01	2.29	2.11655
633244	Drill Core	0.35	<0.01	0.20	<0.01	0.49	2.22833
633245	Drill Core	0.74	<0.01	0.43	<0.01	1.77	2.12523
633246	Drill Core	1.03	<0.01	0.60	<0.01	8.96	2.09842
633247	Drill Core	1.24	<0.01	0.75	<0.01	1.92	1.66528
633248	Drill Core	2.70	<0.01	1.47	<0.01	2.25	2.51134
633249	Drill Core	2.20	<0.01	1.21	<0.01	1.73	2.51557
633250	Drill Core	3.75	<0.01	1.99	<0.01	3.89	2.20515
633251	Drill Core	3.23	<0.01	1.69	<0.01	4.00	2.12206
633252	Drill Core	2.36	<0.01	1.29	<0.01	2.03	2.49432
633253	Drill Core	3.10	<0.01	1.63	<0.01	1.83	2.28402
633254	Drill Core	2.93	<0.01	1.74	<0.01	4.80	2.13839



Acme Analytical Laboratories (Vancouver) Ltd.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: **Selwyn Resources Ltd.**

Suite 700 - 509 Richards Street

Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: November 29, 2010

Page: 1 of 2 Part 1

QUALITY CONTROL REPORT

WHI10000649.1

	Method Analyte Unit MDL	7TD.1	WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD
		Pb	Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg
		%	kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%
		0.02	0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01
Pulp Duplicates																					
633173	Drill Core	13.16	2.51	<0.001	0.005	>10	18.85	4	<0.001	<0.001	0.02	0.49	<0.02	<0.01	0.107	<0.01	<0.01	14.97	0.01	<0.001	0.03
REP 633173	QC	13.02																			
633181	Drill Core	11.82	1.88	<0.001	0.004	>10	13.33	4	<0.001	<0.001	0.04	0.48	<0.02	0.01	0.072	<0.01	0.01	20.52	0.01	0.003	0.05
REP 633181	QC	11.91																			
633193	Drill Core		2.66	<0.001	0.005	<0.02	<0.01	<2	0.010	<0.001	0.01	1.60	<0.02	<0.01	<0.001	<0.01	<0.01	6.15	1.15	0.006	0.50
REP 633193	QC			<0.001	0.005	<0.02	<0.01	<2	0.010	<0.001	0.01	1.58	<0.02	<0.01	<0.001	<0.01	<0.01	6.11	1.14	0.006	0.49
633238	Drill Core		1.26	0.002	0.006	0.14	2.11	<2	0.006	<0.001	<0.01	1.48	<0.02	<0.01	0.004	<0.01	<0.01	2.70	0.20	0.001	0.06
REP 633238	QC			0.002	0.005	0.15	2.13	<2	0.006	<0.001	<0.01	1.48	<0.02	<0.01	0.004	<0.01	<0.01	2.75	0.21	<0.001	0.06
Core Reject Duplicates																					
633172	Drill Core		1.14	<0.001	0.002	3.83	5.42	<2	0.002	<0.001	0.03	2.61	<0.02	0.01	0.025	<0.01	<0.01	17.83	0.03	<0.001	0.07
DUP 633172	QC			<0.001	0.002	3.73	5.21	<2	0.002	<0.001	0.03	2.50	<0.02	0.01	0.024	<0.01	<0.01	17.79	0.03	<0.001	0.06
633207	Drill Core		1.20	0.001	0.022	0.08	0.41	<2	0.008	<0.001	0.01	6.94	<0.02	<0.01	0.002	<0.01	<0.01	3.66	0.08	0.002	0.08
DUP 633207	QC			0.001	0.021	0.08	0.43	<2	0.008	<0.001	0.01	6.43	<0.02	<0.01	0.002	<0.01	<0.01	3.71	0.09	0.001	0.09
633242	Drill Core		1.13	<0.001	0.011	0.21	1.51	2	0.004	<0.001	0.04	6.10	<0.02	0.02	0.004	<0.01	<0.01	25.23	0.02	<0.001	0.10
DUP 633242	QC			<0.001	0.011	0.21	1.41	<2	0.004	<0.001	0.04	5.93	<0.02	0.02	0.004	<0.01	<0.01	25.84	0.03	<0.001	0.10
Reference Materials																					
STD CCU-1C	Standard	0.39																			
STD CCU-1C	Standard	0.40																			
STD CZN-3	Standard	0.08																			
STD CZN-3	Standard	0.09																			
STD OREAS131A	Standard			<0.001	0.033	1.72	2.90	32	0.003	0.002	0.17	5.96	<0.02	<0.01	0.008	<0.01	<0.01	5.47	0.06	0.002	3.11
STD OREAS131A	Standard			<0.001	0.032	1.69	2.91	31	0.003	0.002	0.18	5.87	<0.02	<0.01	0.008	<0.01	<0.01	5.41	0.06	0.003	3.11
STD OREAS131A	Standard			<0.001	0.032	1.69	2.91	31	0.003	0.002	0.17	5.84	<0.02	<0.01	0.008	<0.01	<0.01	5.40	0.06	0.002	3.09
STD OREAS131A	Standard			<0.001	0.032	1.64	2.80	31	0.002	0.002	0.17	5.81	<0.02	<0.01	0.008	<0.01	<0.01	5.32	0.05	0.003	3.02
STD PTC-1A	Standard	0.06																			
STD PTC-1A	Standard	0.05																			
STD R4T	Standard			0.065	0.528	1.62	3.56	91	0.359	0.044	0.09	24.86	<0.02	0.02	0.020	0.02	<0.01	2.23	0.05	0.020	1.45
STD R4T	Standard			0.064	0.512	1.53	3.45	88	0.351	0.041	0.09	24.44	<0.02	0.02	0.019	0.02	<0.01	2.20	0.05	0.020	1.40



Acme Analytical Laboratories (Vancouver) Ltd.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: Selwyn Resources Ltd.

Suite 700 - 509 Richards Street

Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: November 29, 2010

Page: 1 of 2 **Part** 2

QUALITY CONTROL REPORT

WHI10000649.1

Method		7TD	7TD	7TD	7TD	7TD	G8SG
Analyte		Al	Na	K	W	S	SG
Unit		%	%	%	%	%	
MDL		0.01	0.01	0.01	0.01	0.05	0
Pulp Duplicates							
633173	Drill Core	0.07	<0.01	0.03	<0.01	11.71	3.19444
REP 633173	QC						
633181	Drill Core	0.06	<0.01	0.03	<0.01	7.57	3.07415
REP 633181	QC						
633193	Drill Core	2.24	<0.01	1.39	<0.01	1.58	2.14012
REP 633193	QC	2.23	<0.01	1.39	<0.01	1.56	
633238	Drill Core	0.49	<0.01	0.29	<0.01	2.59	2.15065
REP 633238	QC	0.50	<0.01	0.29	<0.01	2.61	
Core Reject Duplicates							
633172	Drill Core	0.26	<0.01	0.13	<0.01	6.48	2.74618
DUP 633172	QC	0.25	<0.01	0.13	<0.01	6.25	2.73899
633207	Drill Core	0.76	<0.01	0.47	<0.01	8.06	2.43191
DUP 633207	QC	0.78	<0.01	0.48	<0.01	7.51	2.44607
633242	Drill Core	0.14	<0.01	0.09	<0.01	8.70	2.60616
DUP 633242	QC	0.14	<0.01	0.11	<0.01	8.42	2.60683
Reference Materials							
STD CCU-1C	Standard						
STD CCU-1C	Standard						
STD CZN-3	Standard						
STD CZN-3	Standard						
STD OREAS131A	Standard	4.61	0.15	3.46	<0.01	4.98	
STD OREAS131A	Standard	4.60	0.16	3.37	<0.01	4.94	
STD OREAS131A	Standard	4.57	0.15	3.31	<0.01	5.02	
STD OREAS131A	Standard	4.46	0.15	3.35	<0.01	4.72	
STD PTC-1A	Standard						
STD PTC-1A	Standard						
STD R4T	Standard	4.00	0.96	1.24	<0.01	13.55	
STD R4T	Standard	3.91	0.94	1.19	<0.01	11.78	



Acme Analytical Laboratories (Vancouver) Ltd.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: Selwyn Resources Ltd.

Suite 700 - 509 Richards Street

Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: November 29, 2010

Page: 2 of 2 Part 1

QUALITY CONTROL REPORT

WHI10000649.1

		7TD.1	WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD
		Pb	Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg
		%	kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%
		0.02	0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.01	0.01
STD R4T	Standard			0.062	0.512	1.53	3.47	88	0.350	0.040	0.09	24.50	<0.02	0.02	0.018	<0.01	<0.01	2.19	0.05	0.019	1.39
STD R4T	Standard			0.066	0.530	1.58	3.57	90	0.359	0.044	0.10	25.00	<0.02	0.02	0.020	0.02	<0.01	2.29	0.06	0.018	1.45
STD SARM 71	Standard	<0.02																			
STD SARM 71	Standard	<0.02																			
STD SU-1B	Standard			<0.001	1.213	<0.02	0.03	7	2.006	0.069	0.07	26.03	<0.02	0.03	<0.001	<0.01	<0.01	2.25	0.08	0.032	1.83
STD SU-1B	Standard			<0.001	1.152	<0.02	0.03	7	1.921	0.065	0.07	25.41	<0.02	0.03	<0.001	<0.01	<0.01	2.26	0.07	0.031	1.79
STD SU-1B	Standard			<0.001	1.191	<0.02	0.03	7	1.997	0.067	0.07	25.77	<0.02	0.03	<0.001	<0.01	<0.01	2.22	0.08	0.031	1.77
STD SU-1B	Standard			<0.001	1.184	<0.02	0.03	7	1.979	0.068	0.07	25.71	<0.02	0.03	<0.001	<0.01	<0.01	2.28	0.07	0.030	1.80
STD R4T Expected				0.062	0.502	1.518	3.376	86	0.339	0.039	0.086	24.07	0.0087	0.0185	0.018	0.0138	0.0018	2.166	0.045	0.018	1.384
STD OREAS131A Expected				0.001	0.0322	1.72	2.83	30.9	0.0027	0.0023	0.1722	5.8166	0.0082	0.0028	0.0081	0.0047	0.001	5.286	0.0536	0.0025	3.1182
STD SU-1B Expected				0.0004	1.185	0.0058	0.0235	6.4	1.97	0.0672	0.0703	25.54	0.00025	0.03	0.0003	0.00002	0.0003	2.21	0.06	0.032	1.79
STD CZN-3 Expected		0.113																			
STD CCU-1C Expected		0.34																			
STD PTC-1A Expected		0.05																			
BLK	Blank			<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	<0.01	<0.01	<0.02	<0.01	<0.001	<0.01	<0.01	<0.01	<0.01	<0.001	<0.01
BLK	Blank			<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	<0.01	<0.01	<0.02	<0.01	<0.001	<0.01	<0.01	<0.01	<0.01	<0.001	<0.01
BLK	Blank			<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	<0.01	<0.01	<0.02	<0.01	<0.001	<0.01	<0.01	<0.01	<0.01	<0.001	<0.01
BLK	Blank			<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	<0.01	<0.01	<0.02	<0.01	<0.001	<0.01	<0.01	<0.01	<0.01	<0.001	<0.01
BLK	Blank	<0.02																			
BLK	Blank	<0.02																			
Prep Wash																					
G1	Prep Blank			<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	0.07	2.40	<0.02	0.08	<0.001	<0.01	<0.01	2.36	0.08	<0.001	0.61
G1	Prep Blank			<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	0.07	2.43	<0.02	0.08	<0.001	<0.01	<0.01	2.37	0.08	<0.001	0.61



Acme Analytical Laboratories (Vancouver) Ltd.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: **Selwyn Resources Ltd.**

Suite 700 - 509 Richards Street

Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: November 29, 2010

Page: 2 of 2 **Part** 2

QUALITY CONTROL REPORT

WHI10000649.1

		7TD Al %	7TD Na %	7TD K %	7TD W %	7TD S %	G8SG SG
		0.01	0.01	0.01	0.01	0.05	0
STD R4T	Standard	3.84	0.94	1.18	<0.01	12.88	
STD R4T	Standard	4.03	0.97	1.23	<0.01	12.78	
STD SARM 71	Standard						
STD SARM 71	Standard						
STD SU-1B	Standard	4.40	1.79	0.65	<0.01	9.52	
STD SU-1B	Standard	4.37	1.76	0.63	<0.01	8.16	
STD SU-1B	Standard	4.34	1.75	0.62	<0.01	9.28	
STD SU-1B	Standard	4.35	1.72	0.63	<0.01	8.73	
STD R4T Expected		3.897	0.9	1.153	0.00016	12.9903	
STD OREAS131A Expected		4.6057	0.1501	3.1584	0.0005	4.8	
STD SU-1B Expected		4.39	1.662	0.6	0.0007	8.76	
STD CZN-3 Expected							
STD CCU-1C Expected							
STD PTC-1A Expected							
BLK	Blank	<0.01	<0.01	<0.01	<0.01	<0.05	
BLK	Blank	<0.01	<0.01	<0.01	<0.01	<0.05	
BLK	Blank	<0.01	<0.01	<0.01	<0.01	<0.05	
BLK	Blank	<0.01	<0.01	<0.01	<0.01	<0.05	
BLK	Blank						
BLK	Blank						
Prep Wash							
G1	Prep Blank	7.93	2.71	3.06	<0.01	<0.05	2.63693
G1	Prep Blank	8.07	2.80	3.02	<0.01	<0.05	2.64712



1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: Selwyn Resources Ltd.

Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Submitted By: Jason K. Dunning

Receiving Lab: Canada-Whitehorse

Received: November 09, 2010

Report Date: November 29, 2010

Page: 1 of 3

CERTIFICATE OF ANALYSIS

WHI10000646.2

CLIENT JOB INFORMATION

Project: Selwyn Project
Shipment ID:
P.O. Number 1014
Number of Samples: 60

SAMPLE DISPOSAL

STOR-PLP Store After 90 days Invoice for Storage
STOR-RJT Store After 90 days Invoice for Storage

Acme does not accept responsibility for samples left at the laboratory after 90 days without prior written instructions for sample storage or return.

Invoice To: Selwyn Resources Ltd.
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6
Canada

CC:

SAMPLE PREPARATION AND ANALYTICAL PROCEDURES

Method Code	Number of Samples	Code Description	Test Wgt (g)	Report Status	Lab
R200-250	58	Crush split and pulverize 250g drill core to 200 mesh			WHI
7TD2	60	4 Acid digestion ICP-ES analysis.	0.5	Completed	VAN
G812	60	Specific Gravity on Pulp		Completed	VAN

ADDITIONAL COMMENTS

Version 2 : Revised decimal places for SG.



This report supersedes all previous preliminary and final reports with this file number dated prior to the date on this certificate. Signature indicates final approval; preliminary reports are unsigned and should be used for reference only.

All results are considered the confidential property of the client. Acme assumes the liabilities for actual cost of analysis only.

“**” asterisk indicates that an analytical result could not be provided due to unusually high levels of interference from other elements.



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: November 29, 2010

Page: 2 of 3 Part 1

CERTIFICATE OF ANALYSIS

WHI10000646.2

	Method Analyte Unit MDL	WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD
		Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg
		kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%
		0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01
633301	Drill Core	4.05	0.001	0.008	<0.02	0.32	<2	0.016	<0.001	<0.01	2.23	<0.02	0.01	0.001	<0.01	<0.01	6.53	1.87	0.010	1.19
633302	Drill Core	1.56	<0.001	0.004	<0.02	<0.01	<2	0.006	<0.001	0.05	1.30	<0.02	0.03	<0.001	<0.01	<0.01	32.22	0.71	0.004	0.39
633303	Drill Core	3.31	<0.001	0.005	<0.02	0.02	<2	0.010	<0.001	0.02	1.87	<0.02	0.02	<0.001	<0.01	<0.01	14.09	1.77	0.008	0.82
633304	Drill Core	2.52	<0.001	0.010	6.08	13.23	14	0.004	<0.001	0.02	3.73	<0.02	<0.01	0.067	<0.01	<0.01	6.49	0.03	0.001	0.14
633305	Drill Core	3.04	<0.001	0.005	0.47	0.34	<2	0.012	<0.001	0.01	1.87	<0.02	0.01	0.001	<0.01	<0.01	7.66	1.64	0.009	0.80
633306	Drill Core	2.36	<0.001	0.003	0.02	0.09	<2	0.007	<0.001	0.01	1.12	<0.02	<0.01	<0.001	<0.01	<0.01	5.30	0.47	0.003	0.13
633307	Drill Core	1.53	0.002	0.006	0.16	0.30	<2	0.011	<0.001	<0.01	1.98	<0.02	<0.01	<0.001	<0.01	<0.01	2.38	0.67	0.004	0.19
633308	Drill Core	1.36	0.002	0.006	0.03	0.21	<2	0.009	<0.001	0.02	1.50	<0.02	<0.01	<0.001	<0.01	<0.01	7.50	0.46	0.003	0.16
633309	Drill Core	1.24	0.004	0.010	0.84	4.74	3	0.009	<0.001	0.01	6.63	<0.02	<0.01	0.020	<0.01	<0.01	2.24	0.04	0.001	0.08
633310	Drill Core	0.41	0.002	0.001	0.06	0.23	<2	0.005	<0.001	0.06	1.14	<0.02	0.02	<0.001	<0.01	<0.01	26.17	0.04	0.001	0.11
633311	Drill Core	0.47	0.002	0.001	0.05	0.36	<2	0.005	<0.001	0.07	1.14	<0.02	0.02	0.001	<0.01	<0.01	26.87	0.03	<0.001	0.11
633312	Drill Core	3.03	0.006	0.014	1.05	8.77	4	0.016	<0.001	0.02	13.42	<0.02	<0.01	0.027	<0.01	<0.01	0.30	0.08	0.004	0.16
633313	Drill Core	2.16	0.003	0.010	2.01	16.44	5	0.009	<0.001	0.01	8.51	<0.02	<0.01	0.068	<0.01	<0.01	0.46	0.04	0.002	0.07
633314	Drill Core	0.83	<0.001	0.006	2.55	16.81	3	0.003	<0.001	<0.01	6.04	<0.02	<0.01	0.092	<0.01	<0.01	0.63	<0.01	<0.001	0.03
633315	Drill Core	1.79	0.001	0.005	2.73	7.19	3	0.006	<0.001	0.02	6.01	<0.02	<0.01	0.030	<0.01	<0.01	5.70	0.03	0.001	0.05
633316	Drill Core	0.91	0.002	0.004	1.07	5.02	<2	0.005	<0.001	0.05	3.82	<0.02	0.01	0.012	<0.01	<0.01	14.18	0.05	0.001	0.09
633317	Drill Core	0.99	0.005	0.005	0.97	5.22	<2	0.008	<0.001	0.04	7.30	<0.02	<0.01	0.012	<0.01	<0.01	11.81	0.08	0.002	0.09
633318	Drill Core	0.62	<0.001	<0.001	0.16	0.51	<2	0.003	<0.001	0.05	0.46	<0.02	0.02	0.001	<0.01	<0.01	30.92	0.03	<0.001	0.09
633319	Drill Core	1.55	<0.001	0.001	0.06	0.62	<2	0.003	<0.001	0.03	0.72	<0.02	0.01	0.002	<0.01	<0.01	17.59	0.03	<0.001	0.05
633320	Rock	0.26	<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	0.02	0.21	<0.02	0.01	<0.001	<0.01	<0.01	21.74	0.04	<0.001	11.56
633321	Drill Core	1.07	0.007	0.007	1.27	3.87	<2	0.012	<0.001	0.01	3.43	<0.02	<0.01	0.011	<0.01	<0.01	4.41	0.06	0.003	0.12
633322	Drill Core	1.11	0.001	0.002	0.20	1.21	<2	0.003	<0.001	0.02	2.76	<0.02	<0.01	0.003	<0.01	<0.01	8.77	0.06	<0.001	0.07
633323	Drill Core	2.53	<0.001	0.001	0.79	1.52	<2	0.002	<0.001	0.06	1.37	<0.02	0.02	0.004	<0.01	<0.01	26.68	0.05	<0.001	0.10
633324	Drill Core	2.68	0.001	0.003	0.43	2.38	<2	0.004	<0.001	0.05	1.49	<0.02	0.01	0.007	<0.01	<0.01	23.85	0.05	0.001	0.09
633325	Drill Core	1.44	0.001	0.004	1.40	5.44	<2	0.007	<0.001	0.02	2.49	<0.02	<0.01	0.016	<0.01	<0.01	3.88	0.08	0.002	0.10
633326	Drill Core	2.75	<0.001	<0.001	0.14	0.32	<2	0.001	<0.001	0.05	0.33	<0.02	0.01	0.001	<0.01	<0.01	34.15	0.03	<0.001	0.08
633327	Drill Core	2.43	0.008	0.006	1.14	2.74	<2	0.016	<0.001	0.01	3.31	<0.02	<0.01	0.008	<0.01	<0.01	1.59	0.06	0.003	0.17
633328	Drill Core	0.81	0.001	<0.001	<0.02	0.03	<2	0.003	<0.001	0.07	0.58	<0.02	0.02	<0.001	<0.01	<0.01	34.76	0.02	<0.001	0.11
633329	Drill Core	0.45	0.005	0.003	0.31	0.48	<2	0.008	<0.001	0.04	2.12	<0.02	0.01	0.001	<0.01	<0.01	15.60	0.03	0.002	0.13
633330	Rock Pulp	0.06	0.002	0.812	0.93	1.31	225	0.002	0.002	0.22	2.77	0.02	0.01	0.009	0.04	<0.01	1.93	<0.01	0.003	0.12



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: November 29, 2010

Page: 2 of 3 **Part** 2

CERTIFICATE OF ANALYSIS

WHI10000646.2

	Method	7TD	7TD	7TD	7TD	G8SG
	Analyte	Na	K	W	S	SG
	Unit	%	%	%	%	
	MDL	0.01	0.01	0.01	0.05	0
633301	Drill Core	<0.01	2.63	<0.01	2.41	2.09
633302	Drill Core	<0.01	0.67	<0.01	1.63	2.39
633303	Drill Core	<0.01	2.14	<0.01	2.03	2.19
633304	Drill Core	<0.01	0.31	<0.01	11.53	2.86
633305	Drill Core	<0.01	2.40	<0.01	2.19	2.18
633306	Drill Core	<0.01	0.74	<0.01	1.16	2.36
633307	Drill Core	<0.01	1.04	<0.01	2.28	2.33
633308	Drill Core	<0.01	0.85	<0.01	1.77	2.37
633309	Drill Core	<0.01	0.54	<0.01	9.88	2.50
633310	Drill Core	<0.01	0.47	<0.01	1.61	2.41
633311	Drill Core	<0.01	0.38	<0.01	1.69	2.35
633312	Drill Core	<0.01	1.27	<0.01	20.07	2.55
633313	Drill Core	<0.01	0.56	<0.01	17.67	2.67
633314	Drill Core	<0.01	0.16	<0.01	14.98	2.75
633315	Drill Core	<0.01	0.27	<0.01	10.83	2.58
633316	Drill Core	<0.01	0.49	<0.01	7.20	2.55
633317	Drill Core	<0.01	0.64	<0.01	11.46	2.55
633318	Drill Core	<0.01	0.15	<0.01	1.02	2.45
633319	Drill Core	<0.01	0.17	<0.01	1.15	2.40
633320	Rock	0.03	0.04	<0.01	0.20	2.63
633321	Drill Core	<0.01	0.75	<0.01	5.98	2.38
633322	Drill Core	<0.01	0.30	<0.01	3.87	2.46
633323	Drill Core	<0.01	0.14	<0.01	2.69	2.49
633324	Drill Core	<0.01	0.19	<0.01	3.20	2.39
633325	Drill Core	<0.01	0.53	<0.01	5.67	2.41
633326	Drill Core	<0.01	0.09	<0.01	0.78	2.45
633327	Drill Core	<0.01	1.25	<0.01	5.29	2.20
633328	Drill Core	<0.01	0.10	<0.01	0.91	2.40
633329	Drill Core	<0.01	0.64	<0.01	2.84	2.26
633330	Rock Pulp	0.58	0.29	<0.01	2.22	N.A.



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: November 29, 2010

Page: 3 of 3 Part 1

CERTIFICATE OF ANALYSIS

WHI10000646.2

	Method Analyte Unit MDL	WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD
		Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg	Al
		kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%	%
		0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01	0.01
633331	Drill Core	0.79	0.002	0.007	2.46	11.63	3	0.004	<0.001	0.04	2.20	<0.02	<0.01	0.039	<0.01	<0.01	12.92	0.04	0.001	0.07	0.41
633332	Drill Core	0.83	0.005	0.007	2.23	9.93	2	0.008	<0.001	0.02	4.95	<0.02	<0.01	0.033	<0.01	<0.01	3.87	0.07	0.003	0.09	0.96
633333	Drill Core	2.09	0.001	0.002	2.80	7.48	2	0.003	<0.001	0.05	1.46	<0.02	0.01	0.026	<0.01	<0.01	21.81	0.04	0.002	0.08	0.24
633334	Drill Core	0.89	0.002	0.005	5.03	14.95	4	0.005	<0.001	0.02	4.57	<0.02	<0.01	0.043	<0.01	<0.01	5.91	0.03	0.002	0.04	0.28
633335	Drill Core	1.59	<0.001	0.003	8.27	22.24	4	0.002	<0.001	<0.01	0.65	<0.02	<0.01	0.091	<0.01	<0.01	2.79	0.03	0.002	0.02	0.15
633336	Drill Core	2.77	0.001	0.003	9.29	22.07	6	0.003	<0.001	<0.01	1.34	<0.02	<0.01	0.076	<0.01	<0.01	1.15	0.03	0.002	0.02	0.22
633337	Drill Core	1.61	<0.001	0.001	3.11	8.37	2	0.001	<0.001	0.03	0.44	<0.02	<0.01	0.032	<0.01	<0.01	22.64	0.02	<0.001	0.05	0.09
633338	Drill Core	2.16	0.001	0.004	6.19	22.91	6	0.003	<0.001	0.02	1.46	<0.02	<0.01	0.072	<0.01	<0.01	10.91	0.04	0.002	0.04	0.24
633339	Drill Core	3.20	0.001	0.004	4.08	19.92	4	0.004	<0.001	0.01	2.56	<0.02	<0.01	0.053	<0.01	<0.01	0.45	0.04	0.001	0.03	0.30
633340	Drill Core	0.77	0.002	0.006	4.83	16.57	4	0.005	<0.001	0.01	3.50	<0.02	<0.01	0.039	<0.01	<0.01	1.53	0.05	0.003	0.05	0.46
633341	Drill Core	0.90	0.003	0.007	5.11	17.11	5	0.007	<0.001	0.01	4.13	<0.02	<0.01	0.039	<0.01	<0.01	1.68	0.05	0.003	0.06	0.52
633342	Drill Core	0.58	0.004	0.008	4.77	13.56	5	0.012	<0.001	0.03	5.45	<0.02	<0.01	0.036	<0.01	<0.01	11.87	0.05	0.003	0.08	0.60
633343	Drill Core	3.06	0.001	0.004	1.92	13.02	3	0.003	<0.001	0.03	2.35	<0.02	0.01	0.032	<0.01	<0.01	20.29	0.02	0.001	0.05	0.21
633344	Drill Core	2.20	0.001	0.004	0.80	4.23	<2	0.005	<0.001	0.04	3.03	<0.02	0.02	0.010	<0.01	<0.01	25.42	0.03	0.002	0.08	0.44
633345	Drill Core	1.98	0.002	0.004	7.59	7.10	5	0.005	<0.001	0.03	2.17	<0.02	<0.01	0.021	<0.01	<0.01	13.00	0.05	0.003	0.08	0.57
633346	Drill Core	1.99	0.005	0.003	0.05	0.73	<2	0.011	<0.001	0.01	2.53	<0.02	<0.01	0.002	<0.01	<0.01	2.65	0.04	0.002	0.11	1.20
633347	Drill Core	2.67	0.001	0.003	0.04	0.19	<2	0.003	<0.001	0.02	0.73	<0.02	<0.01	<0.001	<0.01	<0.01	8.08	0.03	<0.001	0.06	0.33
633348	Drill Core	3.42	0.003	0.007	0.09	0.72	<2	0.009	<0.001	0.02	1.79	<0.02	<0.01	0.002	<0.01	<0.01	9.94	0.28	0.004	0.14	1.05
633349	Drill Core	2.94	0.003	0.011	0.11	0.34	<2	0.013	<0.001	0.02	2.31	<0.02	<0.01	<0.001	<0.01	<0.01	9.72	0.33	0.007	0.26	2.57
633350	Rock	0.29	<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	0.03	0.36	<0.02	0.01	<0.001	<0.01	<0.01	21.51	0.04	<0.001	10.88	0.34
633351	Drill Core	1.34	0.006	0.010	0.22	0.25	<2	0.013	<0.001	0.01	0.69	<0.02	<0.01	<0.001	<0.01	<0.01	5.38	0.21	0.004	0.12	0.88
633352	Drill Core	2.55	0.011	0.017	0.30	1.43	3	0.017	<0.001	0.01	1.76	<0.02	<0.01	0.004	<0.01	<0.01	6.63	0.46	0.006	0.20	1.53
633353	Drill Core	2.37	0.003	0.008	0.16	1.24	<2	0.009	<0.001	0.01	1.62	<0.02	<0.01	0.004	<0.01	<0.01	3.56	0.12	0.001	0.08	0.59
633354	Drill Core	2.90	0.004	0.006	0.45	1.19	3	0.009	<0.001	0.01	0.94	<0.02	<0.01	0.003	<0.01	<0.01	6.96	0.20	0.003	0.09	0.62
633355	Drill Core	1.27	0.006	0.012	2.05	1.99	8	0.015	<0.001	0.01	2.39	<0.02	<0.01	0.005	<0.01	<0.01	2.80	0.31	0.005	0.14	1.20
633356	Drill Core	1.54	0.006	0.011	0.18	1.44	<2	0.015	<0.001	<0.01	2.11	<0.02	<0.01	0.004	<0.01	<0.01	2.32	0.34	0.004	0.12	1.04
633357	Drill Core	1.28	<0.001	0.002	<0.02	<0.01	<2	0.002	<0.001	0.04	1.34	<0.02	0.02	<0.001	<0.01	<0.01	27.58	0.03	0.002	0.28	2.04
633358	Drill Core	2.83	0.004	0.010	0.02	0.01	<2	0.019	<0.001	0.02	3.08	<0.02	<0.01	<0.001	<0.01	<0.01	7.96	0.26	0.010	0.36	3.62
633359	Drill Core	2.56	0.003	0.008	<0.02	0.03	<2	0.019	<0.001	0.01	2.50	<0.02	<0.01	<0.001	<0.01	<0.01	3.53	0.33	0.011	0.33	4.11
633360	Rock Pulp	0.06	<0.001	0.489	1.41	4.31	26	<0.001	0.001	0.69	5.28	<0.02	0.01	0.027	<0.01	<0.01	4.21	0.05	0.004	1.49	4.48



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: November 29, 2010

Page: 3 of 3 **Part** 2

CERTIFICATE OF ANALYSIS

WHI10000646.2

	Method	7TD	7TD	7TD	7TD	G8SG
Analyte	Na	K	W	S	SG	
Unit	%	%	%	%		
MDL	0.01	0.01	0.01	0.05	0	
633331	Drill Core	<0.01	0.23	<0.01	8.87	2.59
633332	Drill Core	<0.01	0.59	<0.01	10.79	2.54
633333	Drill Core	<0.01	0.12	<0.01	5.98	2.56
633334	Drill Core	<0.01	0.15	<0.01	13.20	2.70
633335	Drill Core	<0.01	0.08	<0.01	12.60	2.85
633336	Drill Core	<0.01	0.12	<0.01	13.29	2.87
633337	Drill Core	<0.01	0.05	<0.01	5.28	2.62
633338	Drill Core	<0.01	0.13	<0.01	13.94	3.07
633339	Drill Core	<0.01	0.16	<0.01	12.90	2.90
633340	Drill Core	<0.01	0.26	<0.01	12.43	2.85
633341	Drill Core	<0.01	0.29	<0.01	13.60	2.89
633342	Drill Core	<0.01	0.32	<0.01	13.71	2.91
633343	Drill Core	<0.01	0.11	<0.01	9.71	2.81
633344	Drill Core	<0.01	0.23	<0.01	5.91	2.67
633345	Drill Core	<0.01	0.32	<0.01	7.26	2.80
633346	Drill Core	<0.01	0.66	<0.01	3.05	2.42
633347	Drill Core	<0.01	0.17	<0.01	0.68	2.50
633348	Drill Core	<0.01	0.62	<0.01	2.21	2.48
633349	Drill Core	<0.01	1.64	<0.01	2.65	2.47
633350	Rock	0.03	0.06	<0.01	0.20	2.75
633351	Drill Core	<0.01	0.51	<0.01	0.69	2.45
633352	Drill Core	<0.01	0.87	<0.01	2.65	2.33
633353	Drill Core	<0.01	0.34	<0.01	2.26	2.45
633354	Drill Core	<0.01	0.35	<0.01	1.52	2.40
633355	Drill Core	<0.01	0.69	<0.01	4.12	2.46
633356	Drill Core	<0.01	0.60	<0.01	3.17	2.45
633357	Drill Core	<0.01	1.09	<0.01	1.74	2.60
633358	Drill Core	<0.01	2.44	<0.01	3.67	2.36
633359	Drill Core	<0.01	3.38	<0.01	2.82	2.38
633360	Rock Pulp	0.09	3.34	<0.01	5.28	I.S.



Acme Analytical Laboratories (Vancouver) Ltd.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: **Selwyn Resources Ltd.**

Suite 700 - 509 Richards Street

Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: November 29, 2010

Page: 1 of 1 Part 1

QUALITY CONTROL REPORT

WHI10000646.2

	Method Analyte Unit MDL	WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD
		Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg	Al
		kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%	%
		0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.01	0.001	0.01
Pulp Duplicates																					
633321	Drill Core	1.07	0.007	0.007	1.27	3.87	<2	0.012	<0.001	0.01	3.43	<0.02	<0.01	0.011	<0.01	<0.01	4.41	0.06	0.003	0.12	1.21
REP 633321	QC		0.007	0.007	1.26	3.83	<2	0.012	<0.001	0.01	3.39	<0.02	<0.01	0.011	<0.01	<0.01	4.38	0.06	0.003	0.12	1.20
Core Reject Duplicates																					
633319	Drill Core	1.55	<0.001	0.001	0.06	0.62	<2	0.003	<0.001	0.03	0.72	<0.02	0.01	0.002	<0.01	<0.01	17.59	0.03	<0.001	0.05	0.34
DUP 633319	QC		<0.001	0.001	0.06	0.64	<2	0.003	<0.001	0.03	0.73	<0.02	0.01	0.002	<0.01	<0.01	17.93	0.03	<0.001	0.05	0.33
633354	Drill Core	2.90	0.004	0.006	0.45	1.19	3	0.009	<0.001	0.01	0.94	<0.02	<0.01	0.003	<0.01	<0.01	6.96	0.20	0.003	0.09	0.62
DUP 633354	QC		0.004	0.006	0.44	1.19	3	0.009	<0.001	0.01	0.93	<0.02	<0.01	0.004	<0.01	<0.01	6.85	0.19	0.003	0.09	0.62
Reference Materials																					
STD OREAS131A	Standard		<0.001	0.032	1.70	2.87	31	0.003	0.002	0.18	5.83	<0.02	<0.01	0.008	<0.01	<0.01	5.43	0.06	0.003	3.14	4.58
STD OREAS131A	Standard		<0.001	0.032	1.70	2.88	32	0.003	0.002	0.18	5.92	<0.02	<0.01	0.008	<0.01	<0.01	5.49	0.06	0.002	3.17	4.66
STD OREAS131A	Standard		<0.001	0.033	1.75	2.95	32	0.003	0.002	0.18	6.03	<0.02	<0.01	0.008	<0.01	<0.01	5.54	0.06	0.002	3.16	4.63
STD R4T	Standard		0.063	0.509	1.53	3.43	87	0.355	0.040	0.09	24.56	<0.02	0.02	0.019	0.01	<0.01	2.18	0.05	0.020	1.38	3.78
STD R4T	Standard		0.065	0.516	1.56	3.47	91	0.351	0.041	0.09	24.70	<0.02	0.02	0.019	0.02	<0.01	2.24	0.04	0.018	1.43	4.01
STD R4T	Standard		0.066	0.521	1.59	3.54	91	0.357	0.043	0.09	24.87	<0.02	0.02	0.019	0.01	<0.01	2.23	0.05	0.019	1.45	3.98
STD SU-1B	Standard		<0.001	1.157	<0.02	0.02	7	1.981	0.065	0.07	25.71	<0.02	0.03	<0.001	<0.01	<0.01	2.21	0.06	0.030	1.75	4.31
STD SU-1B	Standard		<0.001	1.183	<0.02	0.02	7	1.985	0.067	0.07	25.97	<0.02	0.03	<0.001	<0.01	<0.01	2.25	0.07	0.030	1.77	4.38
STD SU-1B	Standard		<0.001	1.186	<0.02	0.05	8	1.984	0.068	0.07	26.12	<0.02	0.03	<0.001	<0.01	<0.01	2.25	0.08	0.032	1.83	4.36
STD R4T Expected			0.062	0.502	1.518	3.376	86	0.339	0.039	0.086	24.07	0.0087	0.0185	0.018	0.0138	0.0018	2.166	0.045	0.018	1.384	3.897
STD OREAS131A Expected			0.001	0.0322	1.72	2.83	30.9	0.0027	0.0023	0.1722	5.8166	0.0082	0.0028	0.0081	0.0047	0.001	5.286	0.0536	0.0025	3.1182	4.6057
STD SU-1B Expected			0.0004	1.185	0.0058	0.0235	6.4	1.97	0.0672	0.0703	25.54	0.00025	0.03	0.0003	0.00002	0.0003	2.21	0.06	0.032	1.79	4.39
BLK	Blank		<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	<0.01	<0.01	<0.02	<0.01	<0.001	<0.01	<0.01	<0.01	<0.01	<0.001	<0.01	<0.01
BLK	Blank		<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	<0.01	<0.01	<0.02	<0.01	<0.001	<0.01	<0.01	<0.01	<0.01	<0.001	<0.01	<0.01
BLK	Blank		<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	<0.01	<0.01	<0.02	<0.01	<0.001	<0.01	<0.01	<0.01	<0.01	<0.001	<0.01	<0.01
Prep Wash																					
G1	Prep Blank		<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	0.08	2.51	<0.02	0.08	<0.001	<0.01	<0.01	2.42	0.09	<0.001	0.66	8.33
G1	Prep Blank		<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	0.08	2.59	<0.02	0.08	<0.001	<0.01	<0.01	2.52	0.09	<0.001	0.67	8.32



Acme Analytical Laboratories (Vancouver) Ltd.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: Selwyn Resources Ltd.

Suite 700 - 509 Richards Street

Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: November 29, 2010

Page: 1 of 1 **Part** 2

QUALITY CONTROL REPORT

WHI10000646.2

		Method	7TD	7TD	7TD	7TD	G8SG
		Analyte	Na	K	W	S	SG
		Unit	%	%	%	%	
		MDL	0.01	0.01	0.01	0.05	0
Pulp Duplicates							
633321	Drill Core		<0.01	0.75	<0.01	5.98	2.38
REP 633321	QC		<0.01	0.74	<0.01	5.94	
Core Reject Duplicates							
633319	Drill Core		<0.01	0.17	<0.01	1.15	2.40
DUP 633319	QC		<0.01	0.17	<0.01	1.19	2.42
633354	Drill Core		<0.01	0.35	<0.01	1.52	2.40
DUP 633354	QC		<0.01	0.34	<0.01	1.66	2.45
Reference Materials							
STD OREAS131A	Standard		0.15	3.47	<0.01	5.08	
STD OREAS131A	Standard		0.16	3.61	<0.01	4.98	
STD OREAS131A	Standard		0.16	3.58	<0.01	5.08	
STD R4T	Standard		0.93	1.18	<0.01	13.00	
STD R4T	Standard		0.96	1.23	<0.01	14.41	
STD R4T	Standard		0.95	1.23	<0.01	13.71	
STD SU-1B	Standard		1.70	0.62	<0.01	9.34	
STD SU-1B	Standard		1.75	0.63	<0.01	10.14	
STD SU-1B	Standard		1.78	0.65	<0.01	9.56	
STD R4T Expected			0.9	1.153	0.00016	12.9903	
STD OREAS131A Expected			0.1501	3.1584	0.0005	4.8	
STD SU-1B Expected			1.662	0.6	0.0007	8.76	
BLK	Blank		<0.01	<0.01	<0.01	<0.05	
BLK	Blank		<0.01	<0.01	<0.01	<0.05	
BLK	Blank		<0.01	<0.01	<0.01	<0.05	
Prep Wash							
G1	Prep Blank		2.96	3.22	<0.01	<0.05	2.69
G1	Prep Blank		2.93	3.06	<0.01	<0.05	2.73



1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: Selwyn Resources Ltd.

Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Submitted By: Jason K. Dunning

Receiving Lab: Canada-Whitehorse

Received: November 09, 2010

Report Date: November 26, 2010

Page: 1 of 3

CERTIFICATE OF ANALYSIS

WHI10000646.1

CLIENT JOB INFORMATION

Project: Selwyn Project
Shipment ID:
P.O. Number: 1014
Number of Samples: 60

SAMPLE DISPOSAL

STOR-PLP Store After 90 days Invoice for Storage
STOR-RJT Store After 90 days Invoice for Storage

Acme does not accept responsibility for samples left at the laboratory after 90 days without prior written instructions for sample storage or return.

Invoice To: Selwyn Resources Ltd.
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6
Canada

CC:

SAMPLE PREPARATION AND ANALYTICAL PROCEDURES

Method Code	Number of Samples	Code Description	Test Wgt (g)	Report Status	Lab
R200-250	58	Crush split and pulverize 250g drill core to 200 mesh			WHI
7TD2	60	4 Acid digestion ICP-ES analysis.	0.5	Completed	VAN
G812	60	Specific Gravity on Pulp		Completed	VAN

ADDITIONAL COMMENTS



This report supersedes all previous preliminary and final reports with this file number dated prior to the date on this certificate. Signature indicates final approval; preliminary reports are unsigned and should be used for reference only.
All results are considered the confidential property of the client. Acme assumes the liabilities for actual cost of analysis only.
** asterisk indicates that an analytical result could not be provided due to unusually high levels of interference from other elements.



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: November 26, 2010

Page: 2 of 3 Part 1

CERTIFICATE OF ANALYSIS

WHI10000646.1

	Method Analyte Unit MDL	WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD
		Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg	Al
		kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%	%
		0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01	0.01
633301	Drill Core	4.05	0.001	0.008	<0.02	0.32	<2	0.016	<0.001	<0.01	2.23	<0.02	0.01	0.001	<0.01	<0.01	6.53	1.87	0.010	1.19	3.90
633302	Drill Core	1.56	<0.001	0.004	<0.02	<0.01	<2	0.006	<0.001	0.05	1.30	<0.02	0.03	<0.001	<0.01	<0.01	32.22	0.71	0.004	0.39	1.08
633303	Drill Core	3.31	<0.001	0.005	<0.02	0.02	<2	0.010	<0.001	0.02	1.87	<0.02	0.02	<0.001	<0.01	<0.01	14.09	1.77	0.008	0.82	2.88
633304	Drill Core	2.52	<0.001	0.010	6.08	13.23	14	0.004	<0.001	0.02	3.73	<0.02	<0.01	0.067	<0.01	<0.01	6.49	0.03	0.001	0.14	0.45
633305	Drill Core	3.04	<0.001	0.005	0.47	0.34	<2	0.012	<0.001	0.01	1.87	<0.02	0.01	0.001	<0.01	<0.01	7.66	1.64	0.009	0.80	3.44
633306	Drill Core	2.36	<0.001	0.003	0.02	0.09	<2	0.007	<0.001	0.01	1.12	<0.02	<0.01	<0.001	<0.01	<0.01	5.30	0.47	0.003	0.13	1.18
633307	Drill Core	1.53	0.002	0.006	0.16	0.30	<2	0.011	<0.001	<0.01	1.98	<0.02	<0.01	<0.001	<0.01	<0.01	2.38	0.67	0.004	0.19	1.66
633308	Drill Core	1.36	0.002	0.006	0.03	0.21	<2	0.009	<0.001	0.02	1.50	<0.02	<0.01	<0.001	<0.01	<0.01	7.50	0.46	0.003	0.16	1.33
633309	Drill Core	1.24	0.004	0.010	0.84	4.74	3	0.009	<0.001	0.01	6.63	<0.02	<0.01	0.020	<0.01	<0.01	2.24	0.04	0.001	0.08	0.84
633310	Drill Core	0.41	0.002	0.001	0.06	0.23	<2	0.005	<0.001	0.06	1.14	<0.02	0.02	<0.001	<0.01	<0.01	26.17	0.04	0.001	0.11	0.77
633311	Drill Core	0.47	0.002	0.001	0.05	0.36	<2	0.005	<0.001	0.07	1.14	<0.02	0.02	0.001	<0.01	<0.01	26.87	0.03	<0.001	0.11	0.64
633312	Drill Core	3.03	0.006	0.014	1.05	8.77	4	0.016	<0.001	0.02	13.42	<0.02	<0.01	0.027	<0.01	<0.01	0.30	0.08	0.004	0.16	1.95
633313	Drill Core	2.16	0.003	0.010	2.01	16.44	5	0.009	<0.001	0.01	8.51	<0.02	<0.01	0.068	<0.01	<0.01	0.46	0.04	0.002	0.07	0.86
633314	Drill Core	0.83	<0.001	0.006	2.55	16.81	3	0.003	<0.001	<0.01	6.04	<0.02	<0.01	0.092	<0.01	<0.01	0.63	<0.01	<0.001	0.03	0.29
633315	Drill Core	1.79	0.001	0.005	2.73	7.19	3	0.006	<0.001	0.02	6.01	<0.02	<0.01	0.030	<0.01	<0.01	5.70	0.03	0.001	0.05	0.45
633316	Drill Core	0.91	0.002	0.004	1.07	5.02	<2	0.005	<0.001	0.05	3.82	<0.02	0.01	0.012	<0.01	<0.01	14.18	0.05	0.001	0.09	0.67
633317	Drill Core	0.99	0.005	0.005	0.97	5.22	<2	0.008	<0.001	0.04	7.30	<0.02	<0.01	0.012	<0.01	<0.01	11.81	0.08	0.002	0.09	0.96
633318	Drill Core	0.62	<0.001	<0.001	0.16	0.51	<2	0.003	<0.001	0.05	0.46	<0.02	0.02	0.001	<0.01	<0.01	30.92	0.03	<0.001	0.09	0.28
633319	Drill Core	1.55	<0.001	0.001	0.06	0.62	<2	0.003	<0.001	0.03	0.72	<0.02	0.01	0.002	<0.01	<0.01	17.59	0.03	<0.001	0.05	0.34
633320	Rock	0.26	<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	0.02	0.21	<0.02	0.01	<0.001	<0.01	<0.01	21.74	0.04	<0.001	11.56	0.20
633321	Drill Core	1.07	0.007	0.007	1.27	3.87	<2	0.012	<0.001	0.01	3.43	<0.02	<0.01	0.011	<0.01	<0.01	4.41	0.06	0.003	0.12	1.21
633322	Drill Core	1.11	0.001	0.002	0.20	1.21	<2	0.003	<0.001	0.02	2.76	<0.02	<0.01	0.003	<0.01	<0.01	8.77	0.06	<0.001	0.07	0.43
633323	Drill Core	2.53	<0.001	0.001	0.79	1.52	<2	0.002	<0.001	0.06	1.37	<0.02	0.02	0.004	<0.01	<0.01	26.68	0.05	<0.001	0.10	0.23
633324	Drill Core	2.68	0.001	0.003	0.43	2.38	<2	0.004	<0.001	0.05	1.49	<0.02	0.01	0.007	<0.01	<0.01	23.85	0.05	0.001	0.09	0.34
633325	Drill Core	1.44	0.001	0.004	1.40	5.44	<2	0.007	<0.001	0.02	2.49	<0.02	<0.01	0.016	<0.01	<0.01	3.88	0.08	0.002	0.10	0.90
633326	Drill Core	2.75	<0.001	<0.001	0.14	0.32	<2	0.001	<0.001	0.05	0.33	<0.02	0.01	0.001	<0.01	<0.01	34.15	0.03	<0.001	0.08	0.16
633327	Drill Core	2.43	0.008	0.006	1.14	2.74	<2	0.016	<0.001	0.01	3.31	<0.02	<0.01	0.008	<0.01	<0.01	1.59	0.06	0.003	0.17	1.91
633328	Drill Core	0.81	0.001	<0.001	<0.02	0.03	<2	0.003	<0.001	0.07	0.58	<0.02	0.02	<0.001	<0.01	<0.01	34.76	0.02	<0.001	0.11	0.18
633329	Drill Core	0.45	0.005	0.003	0.31	0.48	<2	0.008	<0.001	0.04	2.12	<0.02	0.01	0.001	<0.01	<0.01	15.60	0.03	0.002	0.13	1.02
633330	Rock Pulp	0.06	0.002	0.812	0.93	1.31	225	0.002	0.002	0.22	2.77	0.02	0.01	0.009	0.04	<0.01	1.93	<0.01	0.003	0.12	1.25



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: November 26, 2010

Page: 2 of 3 **Part** 2

CERTIFICATE OF ANALYSIS

WHI10000646.1

	Method Analyte Unit MDL	7TD	7TD	7TD	7TD	G8SG
		Na	K	W	S	SG
		%	%	%	%	
		0.01	0.01	0.01	0.05	0
633301	Drill Core	<0.01	2.63	<0.01	2.41	2.09418
633302	Drill Core	<0.01	0.67	<0.01	1.63	2.38732
633303	Drill Core	<0.01	2.14	<0.01	2.03	2.19327
633304	Drill Core	<0.01	0.31	<0.01	11.53	2.86027
633305	Drill Core	<0.01	2.40	<0.01	2.19	2.17767
633306	Drill Core	<0.01	0.74	<0.01	1.16	2.36406
633307	Drill Core	<0.01	1.04	<0.01	2.28	2.32911
633308	Drill Core	<0.01	0.85	<0.01	1.77	2.37473
633309	Drill Core	<0.01	0.54	<0.01	9.88	2.49575
633310	Drill Core	<0.01	0.47	<0.01	1.61	2.41179
633311	Drill Core	<0.01	0.38	<0.01	1.69	2.34668
633312	Drill Core	<0.01	1.27	<0.01	20.07	2.55092
633313	Drill Core	<0.01	0.56	<0.01	17.67	2.6692
633314	Drill Core	<0.01	0.16	<0.01	14.98	2.75024
633315	Drill Core	<0.01	0.27	<0.01	10.83	2.58306
633316	Drill Core	<0.01	0.49	<0.01	7.20	2.55465
633317	Drill Core	<0.01	0.64	<0.01	11.46	2.54938
633318	Drill Core	<0.01	0.15	<0.01	1.02	2.45081
633319	Drill Core	<0.01	0.17	<0.01	1.15	2.39747
633320	Rock	0.03	0.04	<0.01	0.20	2.62803
633321	Drill Core	<0.01	0.75	<0.01	5.98	2.37603
633322	Drill Core	<0.01	0.30	<0.01	3.87	2.45968
633323	Drill Core	<0.01	0.14	<0.01	2.69	2.48708
633324	Drill Core	<0.01	0.19	<0.01	3.20	2.38756
633325	Drill Core	<0.01	0.53	<0.01	5.67	2.40629
633326	Drill Core	<0.01	0.09	<0.01	0.78	2.45417
633327	Drill Core	<0.01	1.25	<0.01	5.29	2.19565
633328	Drill Core	<0.01	0.10	<0.01	0.91	2.4028
633329	Drill Core	<0.01	0.64	<0.01	2.84	2.2624
633330	Rock Pulp	0.58	0.29	<0.01	2.22	N.A.



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: November 26, 2010

Page: 3 of 3 Part 1

CERTIFICATE OF ANALYSIS

WHI10000646.1

	Method Analyte Unit MDL	WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD
		Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg	Al
		kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%	%
		0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01	0.01
633331	Drill Core	0.79	0.002	0.007	2.46	11.63	3	0.004	<0.001	0.04	2.20	<0.02	<0.01	0.039	<0.01	<0.01	12.92	0.04	0.001	0.07	0.41
633332	Drill Core	0.83	0.005	0.007	2.23	9.93	2	0.008	<0.001	0.02	4.95	<0.02	<0.01	0.033	<0.01	<0.01	3.87	0.07	0.003	0.09	0.96
633333	Drill Core	2.09	0.001	0.002	2.80	7.48	2	0.003	<0.001	0.05	1.46	<0.02	0.01	0.026	<0.01	<0.01	21.81	0.04	0.002	0.08	0.24
633334	Drill Core	0.89	0.002	0.005	5.03	14.95	4	0.005	<0.001	0.02	4.57	<0.02	<0.01	0.043	<0.01	<0.01	5.91	0.03	0.002	0.04	0.28
633335	Drill Core	1.59	<0.001	0.003	8.27	22.24	4	0.002	<0.001	<0.01	0.65	<0.02	<0.01	0.091	<0.01	<0.01	2.79	0.03	0.002	0.02	0.15
633336	Drill Core	2.77	0.001	0.003	9.29	22.07	6	0.003	<0.001	<0.01	1.34	<0.02	<0.01	0.076	<0.01	<0.01	1.15	0.03	0.002	0.02	0.22
633337	Drill Core	1.61	<0.001	0.001	3.11	8.37	2	0.001	<0.001	0.03	0.44	<0.02	<0.01	0.032	<0.01	<0.01	22.64	0.02	<0.001	0.05	0.09
633338	Drill Core	2.16	0.001	0.004	6.19	22.91	6	0.003	<0.001	0.02	1.46	<0.02	<0.01	0.072	<0.01	<0.01	10.91	0.04	0.002	0.04	0.24
633339	Drill Core	3.20	0.001	0.004	4.08	19.92	4	0.004	<0.001	0.01	2.56	<0.02	<0.01	0.053	<0.01	<0.01	0.45	0.04	0.001	0.03	0.30
633340	Drill Core	0.77	0.002	0.006	4.83	16.57	4	0.005	<0.001	0.01	3.50	<0.02	<0.01	0.039	<0.01	<0.01	1.53	0.05	0.003	0.05	0.46
633341	Drill Core	0.90	0.003	0.007	5.11	17.11	5	0.007	<0.001	0.01	4.13	<0.02	<0.01	0.039	<0.01	<0.01	1.68	0.05	0.003	0.06	0.52
633342	Drill Core	0.58	0.004	0.008	4.77	13.56	5	0.012	<0.001	0.03	5.45	<0.02	<0.01	0.036	<0.01	<0.01	11.87	0.05	0.003	0.08	0.60
633343	Drill Core	3.06	0.001	0.004	1.92	13.02	3	0.003	<0.001	0.03	2.35	<0.02	0.01	0.032	<0.01	<0.01	20.29	0.02	0.001	0.05	0.21
633344	Drill Core	2.20	0.001	0.004	0.80	4.23	<2	0.005	<0.001	0.04	3.03	<0.02	0.02	0.010	<0.01	<0.01	25.42	0.03	0.002	0.08	0.44
633345	Drill Core	1.98	0.002	0.004	7.59	7.10	5	0.005	<0.001	0.03	2.17	<0.02	<0.01	0.021	<0.01	<0.01	13.00	0.05	0.003	0.08	0.57
633346	Drill Core	1.99	0.005	0.003	0.05	0.73	<2	0.011	<0.001	0.01	2.53	<0.02	<0.01	0.002	<0.01	<0.01	2.65	0.04	0.002	0.11	1.20
633347	Drill Core	2.67	0.001	0.003	0.04	0.19	<2	0.003	<0.001	0.02	0.73	<0.02	<0.01	<0.001	<0.01	<0.01	8.08	0.03	<0.001	0.06	0.33
633348	Drill Core	3.42	0.003	0.007	0.09	0.72	<2	0.009	<0.001	0.02	1.79	<0.02	<0.01	0.002	<0.01	<0.01	9.94	0.28	0.004	0.14	1.05
633349	Drill Core	2.94	0.003	0.011	0.11	0.34	<2	0.013	<0.001	0.02	2.31	<0.02	<0.01	<0.001	<0.01	<0.01	9.72	0.33	0.007	0.26	2.57
633350	Rock	0.29	<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	0.03	0.36	<0.02	0.01	<0.001	<0.01	<0.01	21.51	0.04	<0.001	10.88	0.34
633351	Drill Core	1.34	0.006	0.010	0.22	0.25	<2	0.013	<0.001	0.01	0.69	<0.02	<0.01	<0.001	<0.01	<0.01	5.38	0.21	0.004	0.12	0.88
633352	Drill Core	2.55	0.011	0.017	0.30	1.43	3	0.017	<0.001	0.01	1.76	<0.02	<0.01	0.004	<0.01	<0.01	6.63	0.46	0.006	0.20	1.53
633353	Drill Core	2.37	0.003	0.008	0.16	1.24	<2	0.009	<0.001	0.01	1.62	<0.02	<0.01	0.004	<0.01	<0.01	3.56	0.12	0.001	0.08	0.59
633354	Drill Core	2.90	0.004	0.006	0.45	1.19	3	0.009	<0.001	0.01	0.94	<0.02	<0.01	0.003	<0.01	<0.01	6.96	0.20	0.003	0.09	0.62
633355	Drill Core	1.27	0.006	0.012	2.05	1.99	8	0.015	<0.001	0.01	2.39	<0.02	<0.01	0.005	<0.01	<0.01	2.80	0.31	0.005	0.14	1.20
633356	Drill Core	1.54	0.006	0.011	0.18	1.44	<2	0.015	<0.001	<0.01	2.11	<0.02	<0.01	0.004	<0.01	<0.01	2.32	0.34	0.004	0.12	1.04
633357	Drill Core	1.28	<0.001	0.002	<0.02	<0.01	<2	0.002	<0.001	0.04	1.34	<0.02	0.02	<0.001	<0.01	<0.01	27.58	0.03	0.002	0.28	2.04
633358	Drill Core	2.83	0.004	0.010	0.02	0.01	<2	0.019	<0.001	0.02	3.08	<0.02	<0.01	<0.001	<0.01	<0.01	7.96	0.26	0.010	0.36	3.62
633359	Drill Core	2.56	0.003	0.008	<0.02	0.03	<2	0.019	<0.001	0.01	2.50	<0.02	<0.01	<0.001	<0.01	<0.01	3.53	0.33	0.011	0.33	4.11
633360	Rock Pulp	0.06	<0.001	0.489	1.41	4.31	26	<0.001	0.001	0.69	5.28	<0.02	0.01	0.027	<0.01	<0.01	4.21	0.05	0.004	1.49	4.48



Acme Analytical Laboratories (Vancouver) Ltd.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client:

Selwyn Resources Ltd.

Suite 700 - 509 Richards Street

Vancouver BC V6B 2Z6 Canada

Project:

Selwyn Project

Report Date:

November 26, 2010

Page:

3 of 3

Part 2

CERTIFICATE OF ANALYSIS

WHI10000646.1

	Method	7TD	7TD	7TD	7TD	G8SG
Analyte	Na	K	W	S	SG	
Unit	%	%	%	%		
MDL	0.01	0.01	0.01	0.05	0	
633331	Drill Core	<0.01	0.23	<0.01	8.87	2.58507
633332	Drill Core	<0.01	0.59	<0.01	10.79	2.54169
633333	Drill Core	<0.01	0.12	<0.01	5.98	2.5644
633334	Drill Core	<0.01	0.15	<0.01	13.20	2.69937
633335	Drill Core	<0.01	0.08	<0.01	12.60	2.85137
633336	Drill Core	<0.01	0.12	<0.01	13.29	2.87366
633337	Drill Core	<0.01	0.05	<0.01	5.28	2.62109
633338	Drill Core	<0.01	0.13	<0.01	13.94	3.06702
633339	Drill Core	<0.01	0.16	<0.01	12.90	2.89776
633340	Drill Core	<0.01	0.26	<0.01	12.43	2.84927
633341	Drill Core	<0.01	0.29	<0.01	13.60	2.89403
633342	Drill Core	<0.01	0.32	<0.01	13.71	2.91374
633343	Drill Core	<0.01	0.11	<0.01	9.71	2.81024
633344	Drill Core	<0.01	0.23	<0.01	5.91	2.6662
633345	Drill Core	<0.01	0.32	<0.01	7.26	2.80028
633346	Drill Core	<0.01	0.66	<0.01	3.05	2.41629
633347	Drill Core	<0.01	0.17	<0.01	0.68	2.50035
633348	Drill Core	<0.01	0.62	<0.01	2.21	2.48395
633349	Drill Core	<0.01	1.64	<0.01	2.65	2.46851
633350	Rock	0.03	0.06	<0.01	0.20	2.74817
633351	Drill Core	<0.01	0.51	<0.01	0.69	2.4476
633352	Drill Core	<0.01	0.87	<0.01	2.65	2.32529
633353	Drill Core	<0.01	0.34	<0.01	2.26	2.44942
633354	Drill Core	<0.01	0.35	<0.01	1.52	2.39706
633355	Drill Core	<0.01	0.69	<0.01	4.12	2.45592
633356	Drill Core	<0.01	0.60	<0.01	3.17	2.44951
633357	Drill Core	<0.01	1.09	<0.01	1.74	2.59597
633358	Drill Core	<0.01	2.44	<0.01	3.67	2.36249
633359	Drill Core	<0.01	3.38	<0.01	2.82	2.38242
633360	Rock Pulp	0.09	3.34	<0.01	5.28	I.S.



Acme Analytical Laboratories (Vancouver) Ltd.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: **Selwyn Resources Ltd.**

Suite 700 - 509 Richards Street

Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: November 26, 2010

Page: 1 of 1 Part 1

QUALITY CONTROL REPORT

WHI10000646.1

	Method Analyte Unit MDL	WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD
		Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg	Al
		kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%	%
		0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01	0.01
Pulp Duplicates																					
633321	Drill Core	1.07	0.007	0.007	1.27	3.87	<2	0.012	<0.001	0.01	3.43	<0.02	<0.01	0.011	<0.01	<0.01	4.41	0.06	0.003	0.12	1.21
REP 633321	QC		0.007	0.007	1.26	3.83	<2	0.012	<0.001	0.01	3.39	<0.02	<0.01	0.011	<0.01	<0.01	4.38	0.06	0.003	0.12	1.20
Core Reject Duplicates																					
633319	Drill Core	1.55	<0.001	0.001	0.06	0.62	<2	0.003	<0.001	0.03	0.72	<0.02	0.01	0.002	<0.01	<0.01	17.59	0.03	<0.001	0.05	0.34
DUP 633319	QC		<0.001	0.001	0.06	0.64	<2	0.003	<0.001	0.03	0.73	<0.02	0.01	0.002	<0.01	<0.01	17.93	0.03	<0.001	0.05	0.33
633354	Drill Core	2.90	0.004	0.006	0.45	1.19	3	0.009	<0.001	0.01	0.94	<0.02	<0.01	0.003	<0.01	<0.01	6.96	0.20	0.003	0.09	0.62
DUP 633354	QC		0.004	0.006	0.44	1.19	3	0.009	<0.001	0.01	0.93	<0.02	<0.01	0.004	<0.01	<0.01	6.85	0.19	0.003	0.09	0.62
Reference Materials																					
STD OREAS131A	Standard		<0.001	0.032	1.70	2.87	31	0.003	0.002	0.18	5.83	<0.02	<0.01	0.008	<0.01	<0.01	5.43	0.06	0.003	3.14	4.58
STD OREAS131A	Standard		<0.001	0.032	1.70	2.88	32	0.003	0.002	0.18	5.92	<0.02	<0.01	0.008	<0.01	<0.01	5.49	0.06	0.002	3.17	4.66
STD OREAS131A	Standard		<0.001	0.033	1.75	2.95	32	0.003	0.002	0.18	6.03	<0.02	<0.01	0.008	<0.01	<0.01	5.54	0.06	0.002	3.16	4.63
STD R4T	Standard		0.063	0.509	1.53	3.43	87	0.355	0.040	0.09	24.56	<0.02	0.02	0.019	0.01	<0.01	2.18	0.05	0.020	1.38	3.78
STD R4T	Standard		0.065	0.516	1.56	3.47	91	0.351	0.041	0.09	24.70	<0.02	0.02	0.019	0.02	<0.01	2.24	0.04	0.018	1.43	4.01
STD R4T	Standard		0.066	0.521	1.59	3.54	91	0.357	0.043	0.09	24.87	<0.02	0.02	0.019	0.01	<0.01	2.23	0.05	0.019	1.45	3.98
STD SU-1B	Standard		<0.001	1.157	<0.02	0.02	7	1.981	0.065	0.07	25.71	<0.02	0.03	<0.001	<0.01	<0.01	2.21	0.06	0.030	1.75	4.31
STD SU-1B	Standard		<0.001	1.183	<0.02	0.02	7	1.985	0.067	0.07	25.97	<0.02	0.03	<0.001	<0.01	<0.01	2.25	0.07	0.030	1.77	4.38
STD SU-1B	Standard		<0.001	1.186	<0.02	0.05	8	1.984	0.068	0.07	26.12	<0.02	0.03	<0.001	<0.01	<0.01	2.25	0.08	0.032	1.83	4.36
STD R4T Expected			0.062	0.502	1.518	3.376	86	0.339	0.039	0.086	24.07	0.0087	0.0185	0.018	0.0138	0.0018	2.166	0.045	0.018	1.384	3.897
STD OREAS131A Expected			0.001	0.0322	1.72	2.83	30.9	0.0027	0.0023	0.1722	5.8166	0.0082	0.0028	0.0081	0.0047	0.001	5.286	0.0536	0.0025	3.1182	4.6057
STD SU-1B Expected			0.0004	1.185	0.0058	0.0235	6.4	1.97	0.0672	0.0703	25.54	0.00025	0.03	0.0003	0.00002	0.0003	2.21	0.06	0.032	1.79	4.39
BLK	Blank		<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	<0.01	<0.01	<0.02	<0.01	<0.001	<0.01	<0.01	<0.01	<0.01	<0.001	<0.01	<0.01
BLK	Blank		<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	<0.01	<0.01	<0.02	<0.01	<0.001	<0.01	<0.01	<0.01	<0.01	<0.001	<0.01	<0.01
BLK	Blank		<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	<0.01	<0.01	<0.02	<0.01	<0.001	<0.01	<0.01	<0.01	<0.01	<0.001	<0.01	<0.01
Prep Wash																					
G1	Prep Blank		<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	0.08	2.51	<0.02	0.08	<0.001	<0.01	<0.01	2.42	0.09	<0.001	0.66	8.33
G1	Prep Blank		<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	0.08	2.59	<0.02	0.08	<0.001	<0.01	<0.01	2.52	0.09	<0.001	0.67	8.32



Acme Analytical Laboratories (Vancouver) Ltd.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: **Selwyn Resources Ltd.**

Suite 700 - 509 Richards Street

Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: November 26, 2010

Page: 1 of 1 **Part** 2

QUALITY CONTROL REPORT

WHI10000646.1

Method		7TD	7TD	7TD	7TD	G8SG
Analyte		Na	K	W	S	SG
Unit		%	%	%	%	%
MDL		0.01	0.01	0.01	0.05	0
Pulp Duplicates						
633321	Drill Core	<0.01	0.75	<0.01	5.98	2.37603
REP 633321	QC	<0.01	0.74	<0.01	5.94	
Core Reject Duplicates						
633319	Drill Core	<0.01	0.17	<0.01	1.15	2.39747
DUP 633319	QC	<0.01	0.17	<0.01	1.19	2.42269
633354	Drill Core	<0.01	0.35	<0.01	1.52	2.39706
DUP 633354	QC	<0.01	0.34	<0.01	1.66	2.44767
Reference Materials						
STD OREAS131A	Standard	0.15	3.47	<0.01	5.08	
STD OREAS131A	Standard	0.16	3.61	<0.01	4.98	
STD OREAS131A	Standard	0.16	3.58	<0.01	5.08	
STD R4T	Standard	0.93	1.18	<0.01	13.00	
STD R4T	Standard	0.96	1.23	<0.01	14.41	
STD R4T	Standard	0.95	1.23	<0.01	13.71	
STD SU-1B	Standard	1.70	0.62	<0.01	9.34	
STD SU-1B	Standard	1.75	0.63	<0.01	10.14	
STD SU-1B	Standard	1.78	0.65	<0.01	9.56	
STD R4T Expected		0.9	1.153	0.00016	12.9903	
STD OREAS131A Expected		0.1501	3.1584	0.0005	4.8	
STD SU-1B Expected		1.662	0.6	0.0007	8.76	
BLK	Blank	<0.01	<0.01	<0.01	<0.05	
BLK	Blank	<0.01	<0.01	<0.01	<0.05	
BLK	Blank	<0.01	<0.01	<0.01	<0.05	
Prep Wash						
G1	Prep Blank	2.96	3.22	<0.01	<0.05	2.68576
G1	Prep Blank	2.93	3.06	<0.01	<0.05	2.7312



1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: Selwyn Resources Ltd.

Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Submitted By: Jason K. Dunning

Receiving Lab: Canada-Whitehorse

Received: November 08, 2010

Report Date: November 26, 2010

Page: 1 of 5

CERTIFICATE OF ANALYSIS

WHI10000645.1

CLIENT JOB INFORMATION

Project: Selwyn Project
Shipment ID:
P.O. Number 1710-DON-430
Number of Samples: 112

SAMPLE DISPOSAL

STOR-PLP Store After 90 days Invoice for Storage
STOR-RJT Store After 90 days Invoice for Storage

Acme does not accept responsibility for samples left at the laboratory after 90 days without prior written instructions for sample storage or return.

Invoice To: Selwyn Resources Ltd.
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6
Canada

CC:

SAMPLE PREPARATION AND ANALYTICAL PROCEDURES

Method Code	Number of Samples	Code Description	Test Wgt (g)	Report Status	Lab
7TD.1	4	4 Acid digestion ICP-ES analysis	0.1	Completed	VAN
R200-250	109	Crush split and pulverize 250g drill core to 200 mesh			WHI
7TD2	112	4 Acid digestion ICP-ES analysis.	0.5	Completed	VAN
G812	112	Specific Gravity on Pulp		Completed	VAN

ADDITIONAL COMMENTS



This report supersedes all previous preliminary and final reports with this file number dated prior to the date on this certificate. Signature indicates final approval; preliminary reports are unsigned and should be used for reference only.
All results are considered the confidential property of the client. Acme assumes the liabilities for actual cost of analysis only.
** asterisk indicates that an analytical result could not be provided due to unusually high levels of interference from other elements.



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: November 26, 2010

Page: 2 of 5 Part 1

CERTIFICATE OF ANALYSIS

WHI10000645.1

	Method Analyte Unit MDL	7TD.1	WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD
		Pb	Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg
		%	kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%
		0.02	0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01
631251	Drill Core		1.18	<0.001	0.002	0.03	0.09	<2	0.003	<0.001	0.03	0.90	<0.02	0.01	<0.001	<0.01	<0.01	14.44	0.27	<0.001	0.17
631252	Drill Core		3.01	0.002	0.003	0.11	0.49	<2	0.008	<0.001	0.01	1.26	<0.02	<0.01	0.002	<0.01	<0.01	5.32	0.49	0.002	0.14
631253	Drill Core		1.64	0.004	0.005	1.58	4.87	3	0.008	<0.001	0.02	3.94	<0.02	<0.01	0.021	<0.01	<0.01	4.58	0.04	<0.001	0.09
631254	Drill Core		1.79	0.005	0.010	1.76	7.25	2	0.009	<0.001	0.02	4.03	<0.02	<0.01	0.021	<0.01	<0.01	4.66	0.07	0.002	0.11
631255	Drill Core		2.65	<0.001	<0.001	0.77	1.67	<2	<0.001	<0.001	0.06	0.90	<0.02	0.01	0.004	<0.01	<0.01	28.08	0.03	<0.001	0.09
631256	Drill Core		2.63	<0.001	<0.001	0.38	1.23	<2	<0.001	<0.001	0.05	0.44	<0.02	0.01	0.004	<0.01	<0.01	33.83	0.04	<0.001	0.08
631257	Drill Core		1.70	<0.001	0.002	1.06	2.61	2	0.004	<0.001	0.04	3.12	<0.02	0.01	0.008	<0.01	<0.01	19.41	0.07	<0.001	0.10
631258	Drill Core		3.13	0.001	0.002	1.50	5.95	<2	0.005	<0.001	0.02	2.33	<0.02	<0.01	0.016	<0.01	<0.01	2.84	0.08	<0.001	0.10
631259	Drill Core		2.26	<0.001	<0.001	0.29	0.59	<2	0.001	<0.001	0.05	0.61	<0.02	0.01	0.002	<0.01	<0.01	27.69	0.06	<0.001	0.09
631260	Drill Core		0.69	<0.001	<0.001	0.11	0.25	<2	<0.001	<0.001	0.04	0.30	<0.02	0.01	<0.001	<0.01	<0.01	37.32	0.02	<0.001	0.05
631261	Drill Core		0.86	<0.001	<0.001	0.19	0.56	<2	<0.001	<0.001	0.04	0.67	<0.02	0.01	0.002	<0.01	<0.01	34.15	0.02	<0.001	0.05
631262	Drill Core		1.20	0.005	0.014	4.21	14.93	4	0.009	<0.001	0.03	8.10	<0.02	<0.01	0.045	<0.01	<0.01	3.91	0.07	<0.001	0.08
631263	Drill Core		1.59	0.007	0.002	0.06	0.23	<2	0.010	<0.001	<0.01	1.99	<0.02	<0.01	<0.001	<0.01	<0.01	2.53	0.04	0.001	0.12
631264	Drill Core		2.22	0.002	0.004	2.13	11.49	<2	0.003	<0.001	0.04	2.72	<0.02	0.01	0.026	<0.01	<0.01	19.64	0.05	<0.001	0.09
631265	Drill Core		2.27	0.001	0.001	0.34	1.74	<2	0.003	<0.001	0.02	2.84	<0.02	<0.01	0.004	<0.01	<0.01	5.28	0.05	<0.001	0.09
631266	Drill Core		1.37	<0.001	<0.001	0.49	1.92	<2	<0.001	<0.001	0.03	0.85	<0.02	0.01	0.006	<0.01	<0.01	12.31	0.02	<0.001	0.04
631267	Drill Core		0.78	<0.001	0.006	5.43	7.03	3	0.003	<0.001	0.01	4.44	<0.02	<0.01	0.032	<0.01	<0.01	0.35	0.03	<0.001	0.05
631268	Drill Core		0.44	<0.001	0.001	0.11	0.45	<2	<0.001	<0.001	0.09	2.41	<0.02	0.01	0.002	<0.01	<0.01	31.81	0.02	<0.001	0.11
631269	Drill Core		0.78	0.002	0.006	1.01	4.22	3	0.006	<0.001	0.02	3.95	<0.02	<0.01	0.014	<0.01	<0.01	3.81	0.40	0.001	0.11
631270	Rock		0.38	<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	0.02	0.12	<0.02	0.01	<0.001	<0.01	<0.01	21.77	0.02	<0.001	10.78
631271	Drill Core		1.35	<0.001	0.001	<0.02	0.02	<2	0.002	<0.001	0.06	1.34	<0.02	0.01	<0.001	<0.01	<0.01	25.78	0.02	<0.001	0.11
631272	Drill Core		1.21	0.003	0.008	0.18	0.22	2	0.008	<0.001	<0.01	4.67	<0.02	<0.01	<0.001	<0.01	<0.01	1.65	0.30	0.002	0.14
631273	Drill Core		0.63	<0.001	0.002	<0.02	<0.01	<2	<0.001	<0.001	0.02	0.40	<0.02	0.01	<0.001	<0.01	<0.01	18.13	0.11	<0.001	0.04
631274	Drill Core		0.90	0.001	0.002	<0.02	0.07	<2	0.006	<0.001	<0.01	0.99	<0.02	<0.01	<0.001	<0.01	<0.01	3.77	1.41	0.003	0.16
631275	Drill Core		2.20	0.002	0.003	0.04	0.06	<2	0.007	<0.001	<0.01	1.61	<0.02	<0.01	<0.001	<0.01	<0.01	4.31	1.07	0.002	0.12
631276	Drill Core		1.31	0.004	0.010	2.26	7.43	3	0.007	<0.001	0.03	5.49	<0.02	<0.01	0.021	<0.01	<0.01	4.27	0.05	<0.001	0.07
631277	Drill Core		2.75	<0.001	<0.001	0.69	1.46	<2	<0.001	<0.001	0.05	4.94	<0.02	0.02	0.005	<0.01	<0.01	23.51	0.05	<0.001	0.08
631278	Drill Core		2.34	<0.001	<0.001	0.37	1.19	<2	<0.001	<0.001	0.07	1.25	<0.02	0.02	0.004	<0.01	<0.01	35.65	0.03	<0.001	0.11
631279	Drill Core		1.51	<0.001	0.003	<0.02	<0.01	<2	0.003	<0.001	0.01	0.85	<0.02	<0.01	<0.001	<0.01	<0.01	7.17	0.39	0.002	0.09
631280	Rock Pulp		0.02	0.002	0.840	0.94	1.29	219	<0.001	0.002	0.22	2.67	0.02	0.01	0.008	0.03	<0.01	1.95	0.01	0.003	0.12



Acme Analytical Laboratories (Vancouver) Ltd.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: **Selwyn Resources Ltd.**

Suite 700 - 509 Richards Street

Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: November 26, 2010

Page: 2 of 5 Part 2

CERTIFICATE OF ANALYSIS

WHI10000645.1

	Method Analyte Unit MDL	7TD	7TD	7TD	7TD	7TD	G8SG
		Al	Na	K	W	S	SG
		%	%	%	%	%	
		0.01	0.01	0.01	0.01	0.05	0
631251	Drill Core	0.85	<0.01	0.47	<0.01	0.99	2.37
631252	Drill Core	1.40	<0.01	0.80	<0.01	1.54	2.20
631253	Drill Core	1.14	<0.01	0.72	<0.01	6.96	2.40
631254	Drill Core	1.18	<0.01	0.69	<0.01	8.54	2.48
631255	Drill Core	0.27	<0.01	0.15	<0.01	1.97	2.51
631256	Drill Core	0.08	<0.01	0.04	<0.01	1.18	2.51
631257	Drill Core	0.71	<0.01	0.35	<0.01	5.00	2.54
631258	Drill Core	0.95	<0.01	0.52	<0.01	5.63	2.45
631259	Drill Core	0.31	<0.01	0.15	<0.01	0.97	2.48
631260	Drill Core	0.04	<0.01	0.02	<0.01	0.49	2.49
631261	Drill Core	0.10	<0.01	0.05	<0.01	1.08	2.48
631262	Drill Core	0.88	<0.01	0.52	<0.01	17.19	2.72
631263	Drill Core	1.64	<0.01	1.08	<0.01	2.25	2.23
631264	Drill Core	0.57	<0.01	0.26	<0.01	9.17	2.67
631265	Drill Core	0.75	<0.01	0.40	<0.01	3.91	2.46
631266	Drill Core	0.31	<0.01	0.15	<0.01	1.83	2.49
631267	Drill Core	0.51	<0.01	0.26	<0.01	8.95	2.65
631268	Drill Core	0.15	<0.01	0.07	<0.01	3.07	2.48
631269	Drill Core	1.07	<0.01	0.57	<0.01	6.35	2.40
631270	Rock	0.14	<0.01	0.03	<0.01	<0.05	2.65
631271	Drill Core	0.34	<0.01	0.17	<0.01	1.55	2.46
631272	Drill Core	1.14	<0.01	0.64	<0.01	5.20	2.40
631273	Drill Core	0.22	<0.01	0.14	<0.01	0.37	2.50
631274	Drill Core	1.67	<0.01	0.97	<0.01	0.94	2.28
631275	Drill Core	1.36	<0.01	0.83	<0.01	1.65	2.26
631276	Drill Core	0.70	<0.01	0.41	<0.01	10.40	2.50
631277	Drill Core	0.14	<0.01	0.06	<0.01	6.62	2.58
631278	Drill Core	0.08	<0.01	0.04	<0.01	2.09	2.49
631279	Drill Core	0.88	<0.01	0.61	<0.01	0.75	2.41
631280	Rock Pulp	1.25	0.56	0.28	<0.01	2.06	N.A.



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: November 26, 2010

Page: 3 of 5 Part 1

CERTIFICATE OF ANALYSIS

WHI10000645.1

	Method Analyte Unit MDL	7TD.1	WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD
		Pb	Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg
		%	kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%
		0.02	0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01
631281	Drill Core		1.81	0.003	0.010	1.03	7.52	2	0.006	<0.001	0.02	3.69	<0.02	<0.01	0.027	<0.01	<0.01	9.37	0.15	0.002	0.10
631282	Drill Core		1.71	0.001	0.005	1.23	4.04	<2	0.004	<0.001	0.01	2.07	<0.02	<0.01	0.013	<0.01	<0.01	4.23	0.03	0.001	0.07
631283	Drill Core		0.83	<0.001	0.006	5.38	23.65	8	0.003	<0.001	0.02	1.68	<0.02	<0.01	0.075	<0.01	<0.01	14.55	0.03	<0.001	0.07
631284	Drill Core	12.12	1.11	<0.001	0.005	>10	25.46	7	0.001	<0.001	<0.01	0.57	<0.02	<0.01	0.108	<0.01	<0.01	2.53	0.03	<0.001	0.02
631285	Drill Core		1.40	<0.001	0.005	8.23	22.45	7	0.003	<0.001	<0.01	1.32	<0.02	<0.01	0.079	<0.01	<0.01	0.78	0.03	<0.001	0.02
631286	Drill Core		0.55	<0.001	0.004	6.29	25.07	5	0.002	<0.001	<0.01	0.98	<0.02	<0.01	0.077	<0.01	<0.01	0.79	0.03	<0.001	0.02
631287	Drill Core		0.81	0.002	0.003	1.18	4.63	2	0.006	<0.001	0.03	1.91	<0.02	<0.01	0.013	<0.01	<0.01	13.93	0.06	0.002	0.11
631288	Drill Core		2.13	0.003	0.005	1.11	5.92	3	0.007	<0.001	0.04	2.80	<0.02	0.01	0.016	<0.01	<0.01	19.76	0.08	0.003	0.15
631289	Drill Core		0.81	0.003	0.006	2.05	9.10	4	0.009	<0.001	0.03	3.35	<0.02	<0.01	0.027	<0.01	<0.01	8.43	0.08	0.002	0.13
631290	Drill Core		0.75	<0.001	0.004	6.32	16.90	4	0.003	<0.001	0.01	1.08	<0.02	<0.01	0.063	<0.01	<0.01	4.68	0.03	<0.001	0.03
631291	Drill Core		0.69	<0.001	0.005	7.58	19.83	6	0.003	<0.001	<0.01	1.62	<0.02	<0.01	0.074	<0.01	<0.01	2.23	0.02	<0.001	0.03
631292	Drill Core		1.12	<0.001	0.006	8.21	22.40	7	0.004	<0.001	0.02	2.06	<0.02	<0.01	0.090	<0.01	<0.01	7.40	0.05	<0.001	0.06
631293	Drill Core		1.96	0.001	0.010	0.21	1.06	<2	0.005	<0.001	0.02	4.51	<0.02	<0.01	0.004	<0.01	<0.01	11.15	0.17	0.002	0.10
631294	Drill Core		1.00	<0.001	<0.001	0.26	0.17	<2	0.001	<0.001	0.05	1.49	<0.02	0.02	<0.001	<0.01	<0.01	30.31	0.03	<0.001	0.08
631295	Drill Core		2.32	<0.001	0.003	1.75	5.55	<2	0.004	<0.001	0.04	2.33	<0.02	0.01	0.017	<0.01	<0.01	17.81	0.04	0.001	0.09
631296	Drill Core		1.05	<0.001	0.004	4.76	26.87	5	0.003	<0.001	<0.01	1.90	<0.02	<0.01	0.070	0.01	<0.01	1.03	0.04	<0.001	0.03
631297	Drill Core		0.39	<0.001	0.001	6.09	5.09	<2	0.001	<0.001	0.03	0.88	<0.02	0.01	0.029	<0.01	<0.01	25.90	0.02	<0.001	0.06
631298	Drill Core		0.79	<0.001	0.002	8.59	9.74	<2	<0.001	<0.001	0.03	1.04	<0.02	0.01	0.057	<0.01	<0.01	22.97	0.02	<0.001	0.06
631299	Drill Core		1.34	<0.001	0.003	1.57	2.07	<2	0.004	<0.001	0.02	2.16	<0.02	<0.01	0.010	<0.01	<0.01	10.12	0.05	0.001	0.08
631300	Rock		0.38	<0.001	<0.001	0.04	0.04	<2	<0.001	<0.001	0.02	0.18	<0.02	<0.01	<0.001	<0.01	<0.01	21.54	0.03	<0.001	11.45
631301	Drill Core		0.98	0.001	0.004	3.95	0.89	<2	0.006	<0.001	0.03	2.42	<0.02	0.01	0.004	<0.01	<0.01	18.61	0.08	0.002	0.13
631302	Drill Core		1.63	<0.001	0.002	6.89	9.14	<2	<0.001	<0.001	0.03	0.95	<0.02	0.01	0.046	<0.01	<0.01	20.57	0.02	<0.001	0.06
631303	Drill Core	10.57	1.47	<0.001	0.003	>10	17.29	3	<0.001	<0.001	0.03	0.40	<0.02	<0.01	0.084	<0.01	<0.01	20.37	<0.01	<0.001	0.04
631304	Drill Core		0.83	<0.001	0.003	8.33	13.69	2	0.001	<0.001	0.03	0.44	<0.02	<0.01	0.069	<0.01	<0.01	21.12	<0.01	<0.001	0.04
631305	Drill Core		1.57	<0.001	0.001	0.11	0.12	<2	0.003	<0.001	0.04	0.45	<0.02	0.02	<0.001	<0.01	<0.01	30.38	0.03	<0.001	0.07
631306	Drill Core		2.46	<0.001	0.003	0.19	0.08	<2	0.004	<0.001	0.03	0.70	<0.02	0.01	<0.001	<0.01	<0.01	20.01	0.04	<0.001	0.07
631307	Drill Core	14.76	1.64	<0.001	0.003	>10	19.21	4	<0.001	<0.001	0.02	0.66	<0.02	<0.01	0.105	<0.01	<0.01	14.66	0.01	<0.001	0.03
631308	Drill Core		2.14	<0.001	<0.001	0.03	0.06	<2	0.003	<0.001	0.04	0.28	<0.02	0.02	<0.001	<0.01	<0.01	32.07	0.03	<0.001	0.08
631309	Drill Core		2.39	<0.001	0.002	0.10	0.13	<2	0.002	<0.001	0.04	0.29	<0.02	0.02	<0.001	<0.01	<0.01	26.56	0.02	<0.001	0.06
631310	Rock Pulp		0.02	<0.001	0.500	1.47	4.36	30	<0.001	0.001	0.68	5.37	<0.02	0.01	0.027	<0.01	<0.01	4.32	0.05	0.003	1.56



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: Selwyn Resources Ltd.

Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: November 26, 2010

Page: 3 of 5 Part 2

CERTIFICATE OF ANALYSIS

WHI10000645.1

	Method Analyte Unit MDL	7TD	7TD	7TD	7TD	7TD	G8SG
		Al	Na	K	W	S	SG
		%	%	%	%	%	
		0.01	0.01	0.01	0.01	0.05	0
631281	Drill Core	0.94	<0.01	0.52	<0.01	8.20	2.41
631282	Drill Core	0.52	<0.01	0.28	<0.01	4.59	2.37
631283	Drill Core	0.30	<0.01	0.14	<0.01	15.55	2.86
631284	Drill Core	0.11	<0.01	0.06	<0.01	15.51	3.05
631285	Drill Core	0.19	<0.01	0.09	<0.01	14.38	2.80
631286	Drill Core	0.16	<0.01	0.08	<0.01	15.08	2.82
631287	Drill Core	0.81	<0.01	0.41	<0.01	4.77	2.42
631288	Drill Core	1.05	<0.01	0.51	<0.01	6.75	2.45
631289	Drill Core	1.07	<0.01	0.57	<0.01	9.30	2.43
631290	Drill Core	0.25	<0.01	0.13	<0.01	11.23	2.74
631291	Drill Core	0.22	<0.01	0.10	<0.01	13.46	2.78
631292	Drill Core	0.40	<0.01	0.22	<0.01	15.62	2.83
631293	Drill Core	0.60	<0.01	0.33	<0.01	6.01	2.46
631294	Drill Core	0.15	<0.01	0.07	<0.01	1.91	2.49
631295	Drill Core	0.52	<0.01	0.29	<0.01	5.97	2.48
631296	Drill Core	0.20	<0.01	0.09	<0.01	17.03	2.83
631297	Drill Core	0.08	<0.01	0.03	<0.01	4.64	2.68
631298	Drill Core	0.07	<0.01	0.03	<0.01	7.58	2.89
631299	Drill Core	0.57	<0.01	0.29	<0.01	3.85	2.45
631300	Rock	0.15	<0.01	0.04	<0.01	<0.05	2.59
631301	Drill Core	0.93	<0.01	0.46	<0.01	4.06	2.43
631302	Drill Core	0.16	<0.01	0.08	<0.01	7.25	2.80
631303	Drill Core	0.04	<0.01	0.02	<0.01	11.17	3.04
631304	Drill Core	0.09	<0.01	0.04	<0.01	9.10	2.86
631305	Drill Core	0.23	<0.01	0.12	<0.01	0.59	2.34
631306	Drill Core	0.39	<0.01	0.19	<0.01	0.80	2.36
631307	Drill Core	0.07	<0.01	0.04	<0.01	13.00	3.21
631308	Drill Core	0.26	<0.01	0.14	<0.01	0.33	2.39
631309	Drill Core	0.24	<0.01	0.13	<0.01	0.37	2.39
631310	Rock Pulp	4.61	0.10	3.35	<0.01	5.53	N.A.



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: November 26, 2010

Page: 4 of 5 Part 1

CERTIFICATE OF ANALYSIS

WHI10000645.1

	Method Analyte Unit MDL	7TD.1	WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD
		Pb	Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg
		%	kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%
		0.02	0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01
631311	Drill Core		2.18	<0.001	0.003	0.08	0.28	<2	0.005	<0.001	0.03	1.70	<0.02	<0.01	<0.001	<0.01	<0.01	13.54	0.04	<0.001	0.08
631312	Drill Core		2.70	<0.001	0.004	0.04	<0.01	<2	0.005	<0.001	0.02	3.21	<0.02	<0.01	<0.001	<0.01	<0.01	6.46	0.02	<0.001	0.05
631313	Drill Core		1.67	<0.001	0.003	0.02	<0.01	<2	0.004	<0.001	0.02	1.38	<0.02	<0.01	<0.001	<0.01	<0.01	10.99	0.03	<0.001	0.06
631314	Drill Core		1.65	0.002	0.003	0.07	0.19	<2	0.005	<0.001	0.02	0.58	<0.02	<0.01	<0.001	<0.01	<0.01	13.65	0.38	0.001	0.08
631315	Drill Core		0.61	0.006	0.009	0.08	0.59	2	0.011	<0.001	0.03	1.13	<0.02	0.01	0.002	<0.01	<0.01	17.25	0.46	0.004	0.11
631316	Drill Core		1.34	0.007	0.032	0.21	0.35	4	0.013	<0.001	0.01	5.15	<0.02	<0.01	0.001	0.02	<0.01	9.61	0.28	0.004	0.13
631317	Drill Core		0.31	0.013	0.023	0.12	1.90	6	0.018	<0.001	0.01	2.03	<0.02	<0.01	0.006	0.01	<0.01	4.95	0.27	0.007	0.19
631318	Drill Core		1.00	0.010	0.018	0.82	1.67	8	0.018	<0.001	<0.01	4.07	<0.02	<0.01	0.005	<0.01	<0.01	3.76	0.32	0.006	0.17
631319	Drill Core		1.80	0.011	0.015	0.06	1.68	6	0.018	<0.001	<0.01	0.97	<0.02	<0.01	0.006	<0.01	<0.01	2.30	0.09	0.006	0.16
631320	Drill Core		0.86	0.007	0.013	0.04	0.11	3	0.012	<0.001	<0.01	0.78	<0.02	<0.01	<0.001	<0.01	<0.01	2.12	0.24	0.004	0.12
631321	Drill Core		0.81	0.008	0.009	0.04	0.30	4	0.013	<0.001	<0.01	0.65	<0.02	<0.01	<0.001	<0.01	<0.01	1.74	0.25	0.004	0.13
631322	Drill Core		1.27	0.003	0.006	0.15	0.67	3	0.008	<0.001	0.01	0.72	<0.02	<0.01	0.002	<0.01	<0.01	8.11	0.17	0.002	0.08
631323	Drill Core		2.34	0.004	0.005	0.41	1.19	4	0.008	<0.001	0.01	1.03	<0.02	<0.01	0.003	<0.01	<0.01	9.93	1.56	0.002	0.08
631324	Drill Core		0.63	0.001	0.023	0.26	1.47	<2	0.010	<0.001	0.02	9.20	<0.02	<0.01	0.003	<0.01	<0.01	1.80	0.09	<0.001	0.04
631325	Drill Core		1.61	0.002	0.012	0.20	1.93	4	0.010	<0.001	0.03	4.77	<0.02	<0.01	0.005	<0.01	<0.01	7.35	0.08	0.002	0.07
631326	Drill Core		2.99	<0.001	0.004	0.02	<0.01	<2	0.004	<0.001	0.04	1.62	<0.02	0.01	<0.001	<0.01	<0.01	23.31	0.02	<0.001	0.07
631327	Drill Core		1.95	<0.001	0.005	0.02	<0.01	<2	0.005	<0.001	<0.01	0.93	<0.02	<0.01	<0.001	<0.01	<0.01	2.60	0.03	<0.001	0.05
631328	Drill Core		3.04	0.001	0.003	0.02	<0.01	<2	0.006	<0.001	<0.01	2.55	<0.02	<0.01	<0.001	<0.01	<0.01	2.13	0.04	<0.001	0.05
631329	Drill Core		1.93	<0.001	0.004	0.03	<0.01	<2	0.006	<0.001	0.01	3.18	<0.02	<0.01	<0.001	<0.01	<0.01	3.65	0.03	<0.001	0.05
631330	Rock		0.33	<0.001	<0.001	<0.02	<0.01	2	<0.001	<0.001	0.02	0.15	<0.02	0.01	<0.001	<0.01	<0.01	21.37	0.03	<0.001	10.70
631331	Drill Core		2.94	0.001	0.005	0.13	<0.01	3	0.007	<0.001	0.02	3.04	<0.02	<0.01	<0.001	<0.01	<0.01	7.93	0.03	<0.001	0.07
631332	Drill Core	10.68	0.40	0.002	0.002	>10	1.62	20	0.007	<0.001	<0.01	0.80	<0.02	<0.01	0.004	<0.01	<0.01	1.53	0.23	0.002	0.12
631333	Drill Core		2.21	0.003	0.005	0.32	1.58	2	0.009	<0.001	0.03	1.27	<0.02	<0.01	0.004	<0.01	<0.01	9.73	0.28	0.003	0.14
631334	Drill Core		0.81	0.002	0.003	0.18	1.21	2	0.006	<0.001	0.01	1.36	<0.02	<0.01	0.003	<0.01	<0.01	3.09	0.26	0.002	0.06
631335	Drill Core		0.35	0.003	0.005	0.19	0.11	3	0.008	<0.001	0.04	1.00	<0.02	0.01	<0.001	<0.01	<0.01	20.14	0.28	0.002	0.11
631336	Drill Core		0.58	0.003	0.007	0.23	1.59	3	0.010	<0.001	0.02	5.09	<0.02	<0.01	0.004	<0.01	<0.01	4.84	0.51	0.003	0.09
631337	Drill Core		0.26	0.004	0.005	0.44	0.71	3	0.010	<0.001	0.03	3.40	<0.02	<0.01	0.002	<0.01	<0.01	10.80	0.66	0.003	0.14
631338	Drill Core		0.73	0.003	0.003	0.21	2.02	3	0.008	<0.001	0.01	0.65	<0.02	<0.01	0.005	<0.01	<0.01	2.72	0.30	0.003	0.09
631339	Drill Core		0.50	0.002	0.002	0.08	0.37	2	0.007	<0.001	<0.01	0.65	<0.02	<0.01	<0.001	<0.01	<0.01	1.89	0.06	0.001	0.06
631340	Rock Pulp		0.02	0.002	0.863	0.92	1.27	211	0.001	0.002	0.23	2.64	0.02	0.01	0.008	0.03	<0.01	1.93	<0.01	0.003	0.11



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: November 26, 2010

Page: 4 of 5 **Part** 2

CERTIFICATE OF ANALYSIS

WHI10000645.1

	Method Analyte Unit MDL	7TD	7TD	7TD	7TD	7TD	G8SG
		Al	Na	K	W	S	SG
		%	%	%	%	%	
		0.01	0.01	0.01	0.01	0.05	0
631311	Drill Core	0.47	<0.01	0.31	<0.01	2.15	2.43
631312	Drill Core	0.32	<0.01	0.21	<0.01	3.79	2.46
631313	Drill Core	0.34	<0.01	0.19	<0.01	1.46	2.39
631314	Drill Core	0.57	<0.01	0.27	<0.01	0.62	2.38
631315	Drill Core	0.93	<0.01	0.46	<0.01	1.67	2.23
631316	Drill Core	1.02	<0.01	0.54	<0.01	6.15	2.26
631317	Drill Core	1.73	<0.01	0.91	<0.01	3.22	2.02
631318	Drill Core	1.49	<0.01	0.78	<0.01	5.43	2.22
631319	Drill Core	1.46	<0.01	0.79	<0.01	1.75	2.10
631320	Drill Core	1.02	<0.01	0.56	<0.01	0.71	2.12
631321	Drill Core	1.14	<0.01	0.62	<0.01	0.72	2.09
631322	Drill Core	0.54	<0.01	0.30	<0.01	0.89	2.27
631323	Drill Core	0.57	<0.01	0.32	<0.01	1.57	2.33
631324	Drill Core	0.26	<0.01	0.15	<0.01	11.24	2.64
631325	Drill Core	0.51	<0.01	0.29	<0.01	6.36	2.47
631326	Drill Core	0.35	<0.01	0.18	<0.01	1.81	2.46
631327	Drill Core	0.45	<0.01	0.26	<0.01	0.72	2.43
631328	Drill Core	0.45	<0.01	0.25	<0.01	2.51	2.51
631329	Drill Core	0.37	<0.01	0.21	<0.01	3.34	2.50
631330	Rock	0.13	<0.01	0.02	<0.01	<0.05	2.53
631331	Drill Core	0.46	<0.01	0.26	<0.01	3.30	2.53
631332	Drill Core	0.96	<0.01	0.60	<0.01	3.01	2.66
631333	Drill Core	1.02	<0.01	0.60	<0.01	2.08	2.41
631334	Drill Core	0.48	<0.01	0.26	<0.01	1.76	2.42
631335	Drill Core	0.82	<0.01	0.41	<0.01	1.14	2.30
631336	Drill Core	0.67	<0.01	0.39	<0.01	6.33	2.53
631337	Drill Core	0.81	<0.01	0.50	<0.01	4.16	2.51
631338	Drill Core	0.76	<0.01	0.42	<0.01	1.45	2.44
631339	Drill Core	0.52	<0.01	0.29	<0.01	0.51	2.42
631340	Rock Pulp	1.25	0.57	0.27	<0.01	2.00	N.A.



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**

Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: November 26, 2010

Page: 5 of 5 Part 1

CERTIFICATE OF ANALYSIS

WHI10000645.1

	Method Analyte Unit MDL	7TD.1	WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD
		Pb	Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg
		%	kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%
		0.02	0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01
631341	Drill Core		0.99	0.002	0.002	0.75	1.15	3	0.007	<0.001	<0.01	0.74	<0.02	<0.01	0.003	<0.01	<0.01	3.38	0.81	0.002	0.07
631342	Drill Core		1.04	0.003	0.007	0.30	0.48	3	0.009	<0.001	0.06	2.61	<0.02	0.01	0.001	<0.01	<0.01	19.89	0.42	0.003	0.13
631343	Drill Core		0.34	0.004	0.003	0.39	0.38	3	0.008	<0.001	0.04	1.67	<0.02	<0.01	<0.001	<0.01	<0.01	18.29	0.24	0.003	0.16
631344	Drill Core		0.66	<0.001	0.002	0.03	0.04	2	0.002	<0.001	0.05	0.76	<0.02	0.02	<0.001	<0.01	<0.01	34.17	0.05	<0.001	0.14
631345	Drill Core		0.35	0.002	0.003	0.17	1.91	<2	0.007	<0.001	0.03	1.25	<0.02	<0.01	0.005	<0.01	<0.01	11.67	0.38	0.003	0.10
631346	Drill Core		0.45	0.002	0.003	0.09	1.62	2	0.005	<0.001	0.05	0.63	<0.02	0.01	0.004	<0.01	<0.01	23.24	0.05	0.001	0.11
631347	Drill Core		0.72	0.002	0.006	0.79	1.00	4	0.007	<0.001	0.05	0.91	<0.02	0.01	0.003	<0.01	<0.01	19.11	0.08	0.002	0.13
631348	Drill Core		2.09	0.002	0.007	0.63	1.24	4	0.009	<0.001	0.02	0.98	<0.02	<0.01	0.003	<0.01	<0.01	7.04	0.07	0.002	0.12
631349	Drill Core		2.25	<0.001	0.002	0.06	0.35	2	0.004	<0.001	0.01	0.73	<0.02	<0.01	<0.001	<0.01	<0.01	3.17	0.11	<0.001	0.04
631350	Drill Core		0.94	0.001	0.004	0.09	0.51	<2	0.005	<0.001	0.04	1.60	<0.02	0.01	0.001	<0.01	<0.01	19.08	0.04	<0.001	0.08
631351	Drill Core		0.86	0.001	0.004	0.06	0.87	<2	0.005	<0.001	<0.01	1.38	<0.02	<0.01	0.002	<0.01	<0.01	1.67	0.16	<0.001	0.05
631352	Drill Core		2.59	0.002	0.005	0.11	1.02	<2	0.005	<0.001	0.04	0.60	<0.02	0.01	0.002	<0.01	<0.01	24.62	0.03	0.001	0.10
631353	Drill Core		0.92	0.001	0.002	0.05	0.23	<2	0.003	<0.001	0.04	0.43	<0.02	0.01	<0.001	<0.01	<0.01	19.41	0.03	<0.001	0.08
631354	Drill Core		2.81	0.006	0.017	0.26	1.09	<2	0.009	<0.001	0.02	1.25	<0.02	0.02	0.003	<0.01	<0.01	18.94	2.45	0.003	0.09
631355	Drill Core		2.04	0.004	0.013	0.15	0.15	<2	0.007	<0.001	0.04	2.26	<0.02	0.01	<0.001	<0.01	<0.01	23.04	0.18	0.002	0.12
631356	Drill Core		1.14	0.003	0.004	0.13	0.24	<2	0.007	<0.001	0.03	1.19	<0.02	0.01	<0.001	<0.01	<0.01	18.67	0.27	0.002	0.10
631357	Drill Core		1.92	0.004	0.006	0.13	0.40	<2	0.008	<0.001	0.02	1.04	<0.02	<0.01	0.001	<0.01	<0.01	10.23	0.22	0.003	0.10
631358	Drill Core		2.52	0.006	0.009	0.22	1.74	3	0.013	<0.001	<0.01	1.10	<0.02	<0.01	0.005	<0.01	<0.01	2.92	0.31	0.005	0.14
631359	Drill Core		1.13	0.006	0.004	0.15	0.13	<2	0.012	<0.001	<0.01	1.06	<0.02	<0.01	<0.001	<0.01	<0.01	2.73	0.41	0.004	0.11
631360	Rock		0.29	<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	0.02	0.20	<0.02	<0.01	<0.001	<0.01	<0.01	20.83	0.02	<0.001	10.94
631361	Drill Core		0.54	0.007	0.006	0.19	1.18	3	0.014	<0.001	0.01	1.26	<0.02	<0.01	0.004	<0.01	<0.01	3.92	0.17	0.003	0.15
631362	Drill Core		1.13	0.007	0.013	0.04	0.62	<2	0.013	<0.001	0.01	0.93	<0.02	<0.01	0.002	<0.01	<0.01	8.05	0.14	0.003	0.15



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: November 26, 2010

Page: 5 of 5 **Part** 2

CERTIFICATE OF ANALYSIS

WHI10000645.1

	Method Analyte Unit MDL	7TD	7TD	7TD	7TD	7TD	G8SG
		Al	Na	K	W	S	SG
		%	%	%	%	%	
		0.01	0.01	0.01	0.01	0.05	0
631341	Drill Core	0.56	<0.01	0.32	<0.01	1.15	2.43
631342	Drill Core	0.71	<0.01	0.39	<0.01	3.28	2.40
631343	Drill Core	0.89	<0.01	0.49	<0.01	2.11	2.42
631344	Drill Core	0.12	<0.01	0.07	<0.01	0.88	2.58
631345	Drill Core	0.68	<0.01	0.42	<0.01	2.23	2.49
631346	Drill Core	0.59	<0.01	0.31	<0.01	1.46	2.52
631347	Drill Core	0.79	<0.01	0.45	<0.01	1.59	2.55
631348	Drill Core	0.92	<0.01	0.57	<0.01	1.58	2.36
631349	Drill Core	0.23	<0.01	0.13	<0.01	0.70	2.49
631350	Drill Core	0.28	<0.01	0.17	<0.01	2.03	2.50
631351	Drill Core	0.29	<0.01	0.16	<0.01	1.69	2.46
631352	Drill Core	0.46	<0.01	0.28	<0.01	1.10	2.45
631353	Drill Core	0.20	<0.01	0.13	<0.01	0.55	2.45
631354	Drill Core	0.49	<0.01	0.30	<0.01	1.96	2.44
631355	Drill Core	0.51	<0.01	0.31	<0.01	2.76	2.48
631356	Drill Core	0.53	<0.01	0.31	<0.01	1.46	2.39
631357	Drill Core	0.61	<0.01	0.36	<0.01	1.23	2.39
631358	Drill Core	1.09	<0.01	0.61	<0.01	1.89	2.25
631359	Drill Core	0.86	<0.01	0.49	<0.01	0.94	2.34
631360	Rock	0.13	0.02	0.04	<0.01	<0.05	2.59
631361	Drill Core	1.06	<0.01	0.62	<0.01	1.82	2.30
631362	Drill Core	0.90	<0.01	0.56	<0.01	1.25	2.34



Acme Analytical Laboratories (Vancouver) Ltd.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: **Selwyn Resources Ltd.**

Suite 700 - 509 Richards Street

Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: November 26, 2010

Page: 1 of 2 Part 1

QUALITY CONTROL REPORT

WHI10000645.1

	Method Analyte Unit MDL	7TD.1	WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD
		Pb	Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg
		%	kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%
		0.02	0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01
Pulp Duplicates																					
REP 631269	QC			0.002	0.006	0.99	4.21	<2	0.006	<0.001	0.02	3.87	<0.02	<0.01	0.014	<0.01	<0.01	3.81	0.39	0.001	0.11
631303	Drill Core	10.57	1.47	<0.001	0.003	>10	17.29	3	<0.001	<0.001	0.03	0.40	<0.02	<0.01	0.084	<0.01	<0.01	20.37	<0.01	<0.001	0.04
REP 631303	QC	10.54																			
631308	Drill Core		2.14	<0.001	<0.001	0.03	0.06	<2	0.003	<0.001	0.04	0.28	<0.02	0.02	<0.001	<0.01	<0.01	32.07	0.03	<0.001	0.08
REP 631308	QC			<0.001	0.001	0.04	0.06	<2	0.003	<0.001	0.04	0.29	<0.02	0.02	<0.001	<0.01	<0.01	32.80	0.03	<0.001	0.08
631331	Drill Core		2.94	0.001	0.005	0.13	<0.01	3	0.007	<0.001	0.02	3.04	<0.02	<0.01	<0.001	<0.01	<0.01	7.93	0.03	<0.001	0.07
REP 631331	QC			0.001	0.005	0.13	<0.01	3	0.007	<0.001	0.02	2.99	<0.02	<0.01	<0.001	<0.01	<0.01	7.75	0.03	<0.001	0.07
631332	Drill Core	10.68	0.40	0.002	0.002	>10	1.62	20	0.007	<0.001	<0.01	0.80	<0.02	<0.01	0.004	<0.01	<0.01	1.53	0.23	0.002	0.12
REP 631332	QC	10.33																			
Core Reject Duplicates																					
631269	Drill Core		0.78	0.002	0.006	1.01	4.22	3	0.006	<0.001	0.02	3.95	<0.02	<0.01	0.014	<0.01	<0.01	3.81	0.40	0.001	0.11
DUP 631269	QC			0.002	0.006	1.00	4.28	3	0.006	<0.001	0.02	3.85	<0.02	<0.01	0.014	<0.01	<0.01	3.86	0.38	0.001	0.11
631304	Drill Core		0.83	<0.001	0.003	8.33	13.69	2	0.001	<0.001	0.03	0.44	<0.02	<0.01	0.069	<0.01	<0.01	21.12	<0.01	<0.001	0.04
DUP 631304	QC			<0.001	0.002	7.77	12.88	<2	0.001	<0.001	0.03	0.42	<0.02	<0.01	0.064	<0.01	<0.01	21.24	<0.01	<0.001	0.04
631339	Drill Core		0.50	0.002	0.002	0.08	0.37	2	0.007	<0.001	<0.01	0.65	<0.02	<0.01	<0.001	<0.01	<0.01	1.89	0.06	0.001	0.06
DUP 631339	QC			0.002	0.002	0.08	0.39	<2	0.007	<0.001	0.01	0.72	<0.02	<0.01	<0.001	<0.01	<0.01	1.89	0.05	0.001	0.06
Reference Materials																					
STD CCU-1C	Standard	0.40																			
STD CCU-1C	Standard	0.36																			
STD CZN-3	Standard	0.11																			
STD CZN-3	Standard	0.10																			
STD OREAS131A	Standard			<0.001	0.032	1.70	2.88	30	0.002	0.002	0.17	5.83	<0.02	<0.01	0.008	<0.01	<0.01	5.31	0.06	0.003	3.15
STD OREAS131A	Standard			<0.001	0.031	1.75	2.84	31	0.002	0.002	0.17	5.77	<0.02	<0.01	0.008	<0.01	<0.01	5.27	0.06	<0.001	3.15
STD OREAS131A	Standard			<0.001	0.032	1.75	2.86	32	0.002	0.002	0.18	5.81	<0.02	<0.01	0.008	<0.01	<0.01	5.30	0.06	0.002	3.18
STD OREAS131A	Standard			<0.001	0.032	1.71	2.89	31	0.003	0.002	0.17	5.80	<0.02	<0.01	0.008	<0.01	<0.01	5.33	0.05	0.002	3.14
STD PTC-1A	Standard	0.05																			
STD PTC-1A	Standard	0.04																			
STD R4T	Standard			0.062	0.506	1.54	3.42	87	0.354	0.040	0.09	24.25	<0.02	0.02	0.019	0.02	<0.01	2.21	0.05	0.019	1.44



Acme Analytical Laboratories (Vancouver) Ltd.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: Selwyn Resources Ltd.

Suite 700 - 509 Richards Street

Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: November 26, 2010

Page: 1 of 2 **Part** 2

QUALITY CONTROL REPORT

WHI10000645.1

Method		7TD	7TD	7TD	7TD	7TD	G8SG
Analyte		Al	Na	K	W	S	SG
Unit		%	%	%	%	%	
MDL		0.01	0.01	0.01	0.01	0.05	0
Pulp Duplicates							
REP 631269	QC	1.05	<0.01	0.58	<0.01	6.25	
631303	Drill Core	0.04	<0.01	0.02	<0.01	11.17	3.04
REP 631303	QC						
631308	Drill Core	0.26	<0.01	0.14	<0.01	0.33	2.39
REP 631308	QC	0.26	<0.01	0.14	<0.01	0.33	
631331	Drill Core	0.46	<0.01	0.26	<0.01	3.30	2.53
REP 631331	QC	0.45	<0.01	0.26	<0.01	3.24	
631332	Drill Core	0.96	<0.01	0.60	<0.01	3.01	2.66
REP 631332	QC						
Core Reject Duplicates							
631269	Drill Core	1.07	<0.01	0.57	<0.01	6.35	2.40
DUP 631269	QC	1.04	<0.01	0.56	<0.01	6.26	2.40
631304	Drill Core	0.09	<0.01	0.04	<0.01	9.10	2.86
DUP 631304	QC	0.08	<0.01	0.04	<0.01	8.65	2.84
631339	Drill Core	0.52	<0.01	0.29	<0.01	0.51	2.42
DUP 631339	QC	0.52	<0.01	0.28	<0.01	0.52	2.41
Reference Materials							
STD CCU-1C	Standard						
STD CCU-1C	Standard						
STD CZN-3	Standard						
STD CZN-3	Standard						
STD OREAS131A	Standard	4.60	0.15	3.40	<0.01	5.01	
STD OREAS131A	Standard	4.61	0.15	3.40	<0.01	4.63	
STD OREAS131A	Standard	4.62	0.16	3.40	<0.01	4.66	
STD OREAS131A	Standard	4.67	0.15	3.37	<0.01	4.88	
STD PTC-1A	Standard						
STD PTC-1A	Standard						
STD R4T	Standard	3.96	0.93	1.16	<0.01	12.95	



Acme Analytical Laboratories (Vancouver) Ltd.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: Selwyn Resources Ltd.

Suite 700 - 509 Richards Street

Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: November 26, 2010

Page: 2 of 2 Part 1

QUALITY CONTROL REPORT

WHI10000645.1

		7TD.1	WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD
		Pb	Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg
		%	kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%
		0.02	0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.01	0.01
STD R4T	Standard			0.063	0.510	1.60	3.45	99	0.356	0.040	0.09	24.23	<0.02	0.02	0.018	<0.01	<0.01	2.18	0.05	0.018	1.41
STD R4T	Standard			0.064	0.509	1.58	3.43	88	0.356	0.040	0.09	24.22	<0.02	0.02	0.018	0.01	<0.01	2.20	0.05	0.018	1.42
STD R4T	Standard			0.063	0.511	1.54	3.47	88	0.354	0.040	0.09	24.09	<0.02	0.02	0.019	0.02	<0.01	2.18	0.05	0.017	1.43
STD SARM 71	Standard	<0.02																			
STD SARM 71	Standard	<0.02																			
STD SU-1B	Standard			<0.001	1.186	<0.02	0.03	6	1.990	0.066	0.07	25.52	<0.02	0.03	<0.001	<0.01	<0.01	2.27	0.06	0.032	1.81
STD SU-1B	Standard			<0.001	1.184	<0.02	0.03	7	2.003	0.066	0.07	25.54	<0.02	0.03	<0.001	<0.01	<0.01	2.25	0.07	0.031	1.82
STD SU-1B	Standard			<0.001	1.205	<0.02	0.03	9	2.001	0.066	0.07	25.58	<0.02	0.03	<0.001	<0.01	<0.01	2.26	0.06	0.031	1.81
STD SU-1B	Standard			<0.001	1.218	<0.02	0.03	7	2.028	0.067	0.07	25.65	<0.02	0.03	0.001	<0.01	<0.01	2.27	0.06	0.030	1.84
STD R4T Expected				0.062	0.502	1.518	3.376	86	0.339	0.039	0.086	24.07	0.0087	0.0185	0.018	0.0138	0.0018	2.166	0.045	0.018	1.384
STD OREAS131A Expected				0.001	0.0322	1.72	2.83	30.9	0.0027	0.0023	0.1722	5.8166	0.0082	0.0028	0.0081	0.0047	0.001	5.286	0.0536	0.0025	3.1182
STD SU-1B Expected				0.0004	1.185	0.0058	0.0235	6.4	1.97	0.0672	0.0703	25.54	0.00025	0.03	0.0003	0.00002	0.0003	2.21	0.06	0.032	1.79
STD CZN-3 Expected		0.113																			
STD CCU-1C Expected		0.34																			
STD PTC-1A Expected		0.05																			
BLK	Blank			<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	<0.01	<0.01	<0.02	<0.01	<0.001	<0.01	<0.01	<0.01	<0.01	<0.001	<0.01
BLK	Blank			<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	<0.01	<0.01	<0.02	<0.01	<0.001	<0.01	<0.01	<0.01	<0.01	<0.001	<0.01
BLK	Blank			<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	<0.01	<0.01	<0.02	<0.01	<0.001	<0.01	<0.01	<0.01	<0.01	<0.001	<0.01
BLK	Blank			<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	<0.01	<0.01	<0.02	<0.01	<0.001	<0.01	<0.01	<0.01	<0.01	<0.001	<0.01
BLK	Blank	<0.02																			
BLK	Blank	<0.02																			
Prep Wash																					
G1	Prep Blank			<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	0.08	2.38	<0.02	0.08	<0.001	<0.01	<0.01	2.48	0.08	<0.001	0.60
G1	Prep Blank			<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	0.07	2.37	<0.02	0.08	<0.001	<0.01	<0.01	2.51	0.07	<0.001	0.59



Acme Analytical Laboratories (Vancouver) Ltd.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: **Selwyn Resources Ltd.**

Suite 700 - 509 Richards Street

Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: November 26, 2010

Page: 2 of 2 **Part** 2

QUALITY CONTROL REPORT

WHI10000645.1

		7TD Al %	7TD Na %	7TD K %	7TD W %	7TD S %	G8SG SG
		0.01	0.01	0.01	0.01	0.05	0
STD R4T	Standard	3.77	0.92	1.16	<0.01	12.48	
STD R4T	Standard	3.93	0.93	1.15	<0.01	12.29	
STD R4T	Standard	3.98	0.92	1.19	<0.01	14.60	
STD SARM 71	Standard						
STD SARM 71	Standard						
STD SU-1B	Standard	4.38	1.72	0.61	<0.01	9.02	
STD SU-1B	Standard	4.46	1.73	0.61	<0.01	9.19	
STD SU-1B	Standard	4.43	1.75	0.61	<0.01	8.99	
STD SU-1B	Standard	4.51	1.73	0.62	<0.01	10.66	
STD R4T Expected		3.897	0.9	1.153	0.00016	12.9903	
STD OREAS131A Expected		4.6057	0.1501	3.1584	0.0005	4.8	
STD SU-1B Expected		4.39	1.662	0.6	0.0007	8.76	
STD CZN-3 Expected							
STD CCU-1C Expected							
STD PTC-1A Expected							
BLK	Blank	<0.01	<0.01	<0.01	<0.01	<0.05	
BLK	Blank	<0.01	<0.01	<0.01	<0.01	<0.05	
BLK	Blank	<0.01	<0.01	<0.01	<0.01	<0.05	
BLK	Blank	<0.01	<0.01	<0.01	<0.01	<0.05	
BLK	Blank						
BLK	Blank						
Prep Wash							
G1	Prep Blank	8.50	2.86	3.15	<0.01	<0.05	2.58
G1	Prep Blank	8.11	2.85	2.92	<0.01	<0.05	2.55



1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: Selwyn Resources Ltd.

Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Submitted By: Jason K. Dunning

Receiving Lab: Canada-Whitehorse

Received: November 08, 2010

Report Date: November 19, 2010

Page: 1 of 4

CERTIFICATE OF ANALYSIS

WHI10000644.2

CLIENT JOB INFORMATION

Project: Selwyn Project
Shipment ID:
P.O. Number 1710-DON-426
Number of Samples: 63

SAMPLE DISPOSAL

STOR-PLP Store After 90 days Invoice for Storage
STOR-RJT Store After 90 days Invoice for Storage

Acme does not accept responsibility for samples left at the laboratory after 90 days without prior written instructions for sample storage or return.

Invoice To: Selwyn Resources Ltd.
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6
Canada

CC:

SAMPLE PREPARATION AND ANALYTICAL PROCEDURES

Method Code	Number of Samples	Code Description	Test Wgt (g)	Report Status	Lab
R200-250	61	Crush split and pulverize 250g drill core to 200 mesh			WHI
7TD2	63	4 Acid digestion ICP-ES analysis.	0.5	Completed	VAN
G8SG	63	Specific Gravity on Pulp		Completed	VAN

ADDITIONAL COMMENTS

Version 2: DL for G812



This report supersedes all previous preliminary and final reports with this file number dated prior to the date on this certificate. Signature indicates final approval; preliminary reports are unsigned and should be used for reference only.

All results are considered the confidential property of the client. Acme assumes the liabilities for actual cost of analysis only.

“**” asterisk indicates that an analytical result could not be provided due to unusually high levels of interference from other elements.



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: November 19, 2010

Page: 2 of 4 Part 1

CERTIFICATE OF ANALYSIS

WHI10000644.2

	Method Analyte Unit MDL	WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD
		Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg	Al
		kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%	%
		0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01	0.01
632301	Drill Core	2.96	0.001	0.003	<0.02	0.24	<2	0.006	<0.001	0.04	0.98	<0.02	<0.01	<0.001	<0.01	<0.01	14.31	0.44	0.002	0.16	1.00
632302	Drill Core	2.18	0.002	0.004	0.05	0.33	<2	0.011	<0.001	<0.01	1.77	<0.02	<0.01	0.001	<0.01	<0.01	2.15	0.75	0.004	0.19	1.95
632303	Drill Core	1.45	0.005	0.004	0.42	0.05	<2	0.012	<0.001	<0.01	2.09	<0.02	<0.01	<0.001	<0.01	<0.01	1.49	0.10	0.003	0.18	1.83
632304	Drill Core	1.00	0.002	0.013	1.33	2.20	<2	0.004	<0.001	0.03	7.09	<0.02	<0.01	0.020	<0.01	<0.01	11.78	0.02	0.001	0.06	0.44
632305	Drill Core	1.13	<0.001	0.008	5.30	6.54	<2	0.003	<0.001	0.01	4.59	<0.02	<0.01	0.062	<0.01	<0.01	1.38	0.03	0.001	0.07	0.61
632306	Drill Core	0.91	<0.001	0.001	0.07	0.32	<2	0.002	<0.001	0.06	1.01	<0.02	0.02	0.001	<0.01	<0.01	27.05	0.02	<0.001	0.09	0.25
632307	Drill Core	1.88	0.004	0.009	1.24	8.57	<2	0.009	<0.001	0.02	5.86	<0.02	<0.01	0.031	<0.01	<0.01	5.98	0.05	0.002	0.12	1.23
632308	Drill Core	2.65	0.003	0.007	2.05	6.96	<2	0.008	<0.001	0.01	4.76	<0.02	<0.01	0.024	<0.01	<0.01	0.44	0.04	0.002	0.08	0.93
632309	Drill Core	2.15	0.003	0.006	1.06	7.69	<2	0.007	<0.001	0.02	3.65	<0.02	<0.01	0.018	<0.01	<0.01	3.67	0.05	0.001	0.08	0.81
632310	Drill Core	0.30	<0.001	0.002	1.15	2.39	<2	0.002	<0.001	0.07	1.36	<0.02	0.01	0.010	<0.01	<0.01	20.46	0.03	0.001	0.08	0.29
632311	Drill Core	0.39	<0.001	0.002	1.28	2.15	<2	0.002	<0.001	0.06	0.86	<0.02	<0.01	0.009	<0.01	<0.01	19.11	0.03	<0.001	0.08	0.28
632312	Drill Core	2.10	0.001	0.002	0.04	0.97	<2	0.003	<0.001	<0.01	1.68	<0.02	<0.01	0.003	<0.01	<0.01	1.83	0.04	<0.001	0.05	0.49
632313	Drill Core	2.08	0.002	0.003	1.24	3.84	<2	0.004	<0.001	<0.01	1.69	<0.02	<0.01	0.012	<0.01	<0.01	4.09	0.05	<0.001	0.06	0.67
632314	Drill Core	2.35	0.001	0.001	0.03	0.47	<2	0.005	<0.001	<0.01	0.79	<0.02	<0.01	0.001	<0.01	<0.01	3.05	0.04	0.001	0.05	0.57
632315	Drill Core	1.88	0.007	0.003	0.13	0.96	<2	0.012	<0.001	<0.01	1.82	<0.02	<0.01	0.003	<0.01	<0.01	1.68	0.05	0.002	0.13	1.63
632316	Drill Core	2.10	0.007	0.012	1.20	7.59	<2	0.012	<0.001	0.03	5.15	<0.02	<0.01	0.021	<0.01	<0.01	4.43	0.05	0.002	0.12	1.48
632317	Drill Core	2.40	<0.001	<0.001	<0.02	0.02	<2	<0.001	<0.001	0.08	0.50	<0.02	0.02	<0.001	<0.01	<0.01	33.89	0.03	<0.001	0.13	0.15
632318	Drill Core	2.08	<0.001	<0.001	<0.02	0.01	<2	0.001	<0.001	0.08	0.33	<0.02	0.02	<0.001	<0.01	<0.01	35.05	0.04	<0.001	0.14	0.23
632319	Drill Core	3.14	<0.001	<0.001	<0.02	0.01	<2	<0.001	<0.001	0.08	2.87	<0.02	0.02	<0.001	<0.01	<0.01	31.70	0.03	<0.001	0.14	0.17
632320	Rock	0.39	<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	0.01	0.12	<0.02	0.01	<0.001	<0.01	<0.01	20.73	0.03	<0.001	10.92	0.13
632321	Drill Core	1.52	<0.001	<0.001	<0.02	0.01	<2	0.001	<0.001	0.07	0.28	<0.02	0.02	<0.001	<0.01	<0.01	34.00	0.03	<0.001	0.10	0.16
632322	Drill Core	1.56	<0.001	<0.001	<0.02	<0.01	<2	0.002	<0.001	0.03	0.44	<0.02	<0.01	<0.001	<0.01	<0.01	18.59	0.05	<0.001	0.07	0.30
632323	Drill Core	0.64	<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	0.09	0.35	<0.02	0.02	<0.001	<0.01	<0.01	34.82	0.04	<0.001	0.19	0.14
632324	Drill Core	1.16	0.001	0.005	0.80	2.72	<2	0.007	<0.001	0.02	14.80	<0.02	<0.01	0.007	<0.01	<0.01	3.63	0.12	0.002	0.10	0.85
632325	Drill Core	2.84	0.001	0.003	1.79	4.58	<2	0.006	<0.001	0.02	2.15	<0.02	<0.01	0.012	<0.01	<0.01	3.72	0.08	0.001	0.11	0.90
632326	Drill Core	3.03	0.001	0.002	0.74	3.84	<2	0.002	<0.001	0.05	2.24	<0.02	0.01	0.011	<0.01	<0.01	27.63	0.04	0.001	0.09	0.38
632327	Drill Core	1.17	0.002	0.003	0.32	1.40	<2	0.007	<0.001	0.02	2.11	<0.02	<0.01	0.004	<0.01	<0.01	8.27	0.09	0.001	0.11	0.87
632328	Drill Core	1.07	0.001	0.002	1.45	2.60	<2	0.005	<0.001	0.02	4.58	<0.02	<0.01	0.007	<0.01	<0.01	4.34	0.04	0.002	0.10	0.69
632329	Drill Core	1.47	<0.001	0.005	3.80	28.02	5	0.002	<0.001	0.02	1.26	<0.02	<0.01	0.069	<0.01	<0.01	12.39	0.04	<0.001	0.04	0.23
632330	Rock Pulp	0.02	0.002	0.813	0.92	1.26	216	0.002	0.002	0.23	2.58	<0.02	0.01	0.008	0.02	<0.01	1.92	0.01	0.003	0.12	1.25



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: November 19, 2010

Page: 2 of 4 **Part** 2

CERTIFICATE OF ANALYSIS

WHI10000644.2

	Method Analyte Unit MDL	7TD	7TD	7TD	7TD	G8SG
		Na	K	W	S	SG
		%	%	%	%	
		0.01	0.01	0.01	0.05	0
632301	Drill Core	<0.01	0.52	<0.01	1.17	2.46
632302	Drill Core	<0.01	1.02	<0.01	2.05	2.39
632303	Drill Core	<0.01	0.95	<0.01	2.39	2.41
632304	Drill Core	<0.01	0.24	<0.01	9.72	2.88
632305	Drill Core	<0.01	0.32	<0.01	8.76	2.84
632306	Drill Core	<0.01	0.13	<0.01	1.29	2.53
632307	Drill Core	<0.01	0.67	<0.01	11.01	2.74
632308	Drill Core	<0.01	0.47	<0.01	9.03	2.64
632309	Drill Core	<0.01	0.44	<0.01	7.93	2.63
632310	Drill Core	<0.01	0.14	<0.01	2.78	2.70
632311	Drill Core	<0.01	0.14	<0.01	2.11	2.67
632312	Drill Core	<0.01	0.23	<0.01	2.06	2.51
632313	Drill Core	<0.01	0.36	<0.01	3.82	2.64
632314	Drill Core	<0.01	0.29	<0.01	0.87	2.45
632315	Drill Core	<0.01	0.89	<0.01	2.35	2.35
632316	Drill Core	<0.01	0.88	<0.01	9.69	2.56
632317	Drill Core	<0.01	0.07	<0.01	0.54	2.62
632318	Drill Core	<0.01	0.11	<0.01	0.35	2.59
632319	Drill Core	<0.01	0.08	<0.01	3.24	2.62
632320	Rock	<0.01	0.02	<0.01	<0.05	2.75
632321	Drill Core	<0.01	0.07	<0.01	0.39	2.53
632322	Drill Core	<0.01	0.14	<0.01	0.34	2.55
632323	Drill Core	<0.01	0.07	<0.01	0.37	2.66
632324	Drill Core	<0.01	0.46	<0.01	17.88	2.86
632325	Drill Core	<0.01	0.48	<0.01	4.78	2.58
632326	Drill Core	<0.01	0.17	<0.01	4.48	2.64
632327	Drill Core	<0.01	0.47	<0.01	2.96	2.50
632328	Drill Core	<0.01	0.36	<0.01	6.56	2.65
632329	Drill Core	<0.01	0.12	<0.01	16.22	3.10
632330	Rock Pulp	0.57	0.28	<0.01	2.04	I.S.



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: November 19, 2010

Page: 3 of 4 Part 1

CERTIFICATE OF ANALYSIS

WHI10000644.2

	Method Analyte Unit MDL	WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD
		Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg	Al
		kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%	%
		0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01	0.01
632331	Drill Core	1.57	0.002	0.004	2.15	5.57	3	0.006	<0.001	0.03	3.57	<0.02	<0.01	0.014	<0.01	<0.01	11.53	0.06	0.002	0.10	0.70
632332	Drill Core	1.78	0.002	0.004	2.48	9.59	3	0.006	<0.001	0.02	2.39	<0.02	<0.01	0.030	<0.01	<0.01	4.75	0.07	0.002	0.09	0.72
632333	Drill Core	0.82	0.001	0.006	1.41	12.63	4	0.003	<0.001	0.04	1.73	<0.02	0.01	0.027	<0.01	<0.01	20.55	0.03	0.001	0.07	0.35
632334	Drill Core	2.63	<0.001	0.002	0.38	1.84	<2	0.003	<0.001	0.04	0.78	<0.02	0.02	0.004	<0.01	<0.01	31.24	0.07	0.001	0.11	0.47
632335	Drill Core	2.61	<0.001	0.002	0.03	0.08	<2	0.004	<0.001	0.04	0.85	<0.02	0.02	<0.001	<0.01	<0.01	29.34	0.06	0.001	0.13	0.66
632336	Drill Core	1.90	<0.001	0.002	<0.02	0.02	<2	0.003	<0.001	0.04	0.97	<0.02	0.02	<0.001	<0.01	<0.01	30.98	0.04	0.001	0.12	0.53
632337	Drill Core	2.39	0.003	0.004	0.34	1.86	<2	0.008	<0.001	0.02	1.47	<0.02	<0.01	0.004	<0.01	<0.01	6.52	0.08	0.002	0.13	1.17
632338	Drill Core	0.90	0.003	0.011	1.62	9.27	4	0.009	<0.001	<0.01	3.74	<0.02	<0.01	0.023	<0.01	<0.01	1.77	0.05	0.002	0.08	0.74
632339	Drill Core	2.00	0.001	0.002	0.07	0.06	<2	0.005	<0.001	<0.01	1.38	<0.02	<0.01	<0.001	<0.01	<0.01	1.81	0.04	0.001	0.07	0.51
632340	Drill Core	1.05	<0.001	0.002	0.04	0.08	<2	0.003	<0.001	0.05	0.65	<0.02	0.02	<0.001	<0.01	<0.01	31.34	0.05	0.001	0.11	0.53
632341	Drill Core	1.35	<0.001	0.002	0.04	0.09	<2	0.003	<0.001	0.05	0.57	<0.02	0.02	<0.001	<0.01	<0.01	31.54	0.06	0.001	0.11	0.53
632342	Drill Core	2.70	0.002	0.004	0.47	0.71	<2	0.006	<0.001	0.01	0.74	<0.02	<0.01	0.002	<0.01	<0.01	3.81	0.06	0.002	0.08	0.60
632343	Drill Core	1.95	0.003	0.008	0.06	0.65	3	0.009	<0.001	0.04	4.53	<0.02	<0.01	0.002	<0.01	<0.01	11.66	0.37	0.003	0.10	0.64
632344	Drill Core	0.74	0.005	0.006	0.05	4.45	3	0.016	<0.001	<0.01	4.47	<0.02	<0.01	0.015	<0.01	<0.01	1.23	0.26	0.004	0.13	1.01
632345	Drill Core	2.44	0.007	0.019	0.06	0.75	3	0.012	<0.001	0.03	1.90	<0.02	0.01	0.003	<0.01	<0.01	18.95	1.49	0.006	0.11	0.75
632346	Drill Core	1.54	0.006	0.010	0.03	0.22	3	0.009	<0.001	0.05	4.67	<0.02	0.01	<0.001	<0.01	<0.01	21.36	0.12	0.003	0.18	0.58
632347	Drill Core	1.64	0.005	0.007	0.03	0.25	<2	0.007	<0.001	0.05	1.71	<0.02	0.02	0.001	<0.01	<0.01	23.05	0.11	0.002	0.16	0.63
632348	Drill Core	1.54	0.001	0.004	0.12	0.06	2	0.004	<0.001	0.08	1.34	<0.02	0.02	<0.001	<0.01	<0.01	33.86	0.02	<0.001	0.16	0.18
632349	Drill Core	2.34	0.004	0.008	1.24	0.17	9	0.006	<0.001	0.03	4.23	<0.02	<0.01	<0.001	<0.01	<0.01	17.32	0.20	0.002	0.09	0.45
632350	Rock	0.34	<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	0.01	0.16	<0.02	<0.01	<0.001	<0.01	<0.01	21.41	0.04	<0.001	11.42	0.18
632351	Drill Core	1.19	0.004	0.016	0.12	0.59	3	0.008	<0.001	0.03	1.71	<0.02	0.01	0.002	<0.01	<0.01	21.77	0.31	0.004	0.13	0.70
632352	Drill Core	1.64	0.003	0.009	0.08	0.41	3	0.007	<0.001	0.02	1.11	<0.02	<0.01	0.002	<0.01	<0.01	13.30	0.21	0.003	0.08	0.45
632353	Drill Core	0.80	0.005	0.010	0.37	0.41	5	0.011	<0.001	<0.01	0.64	<0.02	<0.01	0.002	<0.01	<0.01	7.54	1.10	0.004	0.10	0.75
632354	Drill Core	1.15	0.005	0.055	0.43	0.93	7	0.013	<0.001	<0.01	7.79	<0.02	<0.01	0.003	<0.01	<0.01	4.49	0.23	0.005	0.11	0.86
632355	Drill Core	2.16	0.008	0.017	0.10	0.46	3	0.016	<0.001	0.01	1.03	<0.02	<0.01	0.002	<0.01	<0.01	6.52	0.23	0.005	0.15	1.20
632356	Drill Core	2.67	0.011	0.016	0.06	0.46	5	0.021	<0.001	<0.01	1.35	<0.02	<0.01	0.002	<0.01	<0.01	1.68	0.11	0.006	0.17	1.42
632357	Drill Core	1.65	0.004	0.028	0.15	0.31	5	0.026	<0.001	<0.01	4.45	<0.02	<0.01	0.001	<0.01	<0.01	7.17	2.25	0.016	0.25	2.10
632358	Drill Core	2.10	<0.001	0.003	<0.02	<0.01	<2	0.004	<0.001	0.04	1.72	<0.02	0.02	<0.001	<0.01	<0.01	21.44	0.38	0.004	0.36	2.65
632359	Drill Core	2.69	<0.001	0.002	<0.02	<0.01	<2	0.002	<0.001	0.04	1.46	<0.02	0.02	<0.001	<0.01	<0.01	26.98	0.02	0.003	0.40	2.59
632360	Rock Pulp	0.02	<0.001	0.497	1.51	4.34	29	0.001	0.001	0.70	5.33	<0.02	0.01	0.027	<0.01	<0.01	4.25	0.05	0.004	1.56	4.47



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: November 19, 2010

Page: 3 of 4 **Part** 2

CERTIFICATE OF ANALYSIS

WHI10000644.2

	Method	7TD	7TD	7TD	7TD	G8SG
	Analyte	Na	K	W	S	SG
	Unit	%	%	%	%	
	MDL	0.01	0.01	0.01	0.05	0
632331	Drill Core	<0.01	0.39	<0.01	7.74	2.73
632332	Drill Core	<0.01	0.39	<0.01	8.09	2.72
632333	Drill Core	<0.01	0.18	<0.01	8.79	2.85
632334	Drill Core	<0.01	0.23	<0.01	1.93	2.54
632335	Drill Core	<0.01	0.33	<0.01	1.09	2.47
632336	Drill Core	<0.01	0.26	<0.01	1.17	2.55
632337	Drill Core	<0.01	0.71	<0.01	2.64	2.42
632338	Drill Core	<0.01	0.43	<0.01	9.36	2.65
632339	Drill Core	<0.01	0.28	<0.01	1.38	2.52
632340	Drill Core	<0.01	0.27	<0.01	0.79	2.46
632341	Drill Core	<0.01	0.27	<0.01	0.70	2.56
632342	Drill Core	<0.01	0.33	<0.01	1.01	2.54
632343	Drill Core	<0.01	0.37	<0.01	5.71	2.56
632344	Drill Core	<0.01	0.55	<0.01	7.27	2.54
632345	Drill Core	<0.01	0.38	<0.01	2.59	2.38
632346	Drill Core	<0.01	0.30	<0.01	5.69	2.60
632347	Drill Core	<0.01	0.32	<0.01	2.14	2.50
632348	Drill Core	<0.01	0.09	<0.01	1.67	2.56
632349	Drill Core	<0.01	0.23	<0.01	5.27	2.65
632350	Rock	0.01	0.04	<0.01	<0.05	2.72
632351	Drill Core	<0.01	0.36	<0.01	2.26	2.48
632352	Drill Core	<0.01	0.25	<0.01	1.45	2.50
632353	Drill Core	<0.01	0.43	<0.01	0.84	2.41
632354	Drill Core	<0.01	0.49	<0.01	9.67	2.55
632355	Drill Core	<0.01	0.68	<0.01	1.33	2.34
632356	Drill Core	<0.01	0.81	<0.01	1.60	2.32
632357	Drill Core	<0.01	1.23	<0.01	5.19	2.36
632358	Drill Core	<0.01	1.40	<0.01	1.94	2.54
632359	Drill Core	<0.01	1.39	<0.01	1.59	2.61
632360	Rock Pulp	0.09	3.30	<0.01	5.00	N.A.



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: November 19, 2010

Page: 4 of 4 **Part** 1

CERTIFICATE OF ANALYSIS

WHI10000644.2

	Method	WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD
	Analyte	Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg
	Unit	kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%
	MDL	0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01
632361	Drill Core	2.34	0.002	0.004	<0.02	<0.01	<2	0.008	<0.001	0.04	2.68	<0.02	0.01	<0.001	<0.01	<0.01	19.82	0.02	0.004	0.47
632362	Drill Core	2.42	0.005	0.006	<0.02	<0.01	<2	0.012	<0.001	0.01	3.46	<0.02	0.03	<0.001	<0.01	<0.01	22.44	8.21	0.007	0.19
632363	Drill Core	1.81	0.011	0.011	<0.02	0.09	7	0.031	0.001	<0.01	2.92	<0.02	<0.01	<0.001	<0.01	<0.01	1.45	0.27	0.017	0.52



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**

Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: November 19, 2010

Page: 4 of 4 Part 2

CERTIFICATE OF ANALYSIS

WHI10000644.2

		Method	7TD	7TD	7TD	7TD	G8SG
		Analyte	Na	K	W	S	SG
		Unit	%	%	%	%	
		MDL	0.01	0.01	0.01	0.05	0
632361	Drill Core		<0.01	1.74	<0.01	3.00	2.58
632362	Drill Core		0.02	0.90	<0.01	3.97	2.64
632363	Drill Core		<0.01	2.94	<0.01	3.28	2.23



Acme Analytical Laboratories (Vancouver) Ltd.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: Selwyn Resources Ltd.

Suite 700 - 509 Richards Street

Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: November 19, 2010

Page: 1 of 1 Part 1

QUALITY CONTROL REPORT

WHI10000644.2

	Method Analyte Unit MDL	WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD
		Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg	Al
		kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%	%
		0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01	0.01
Pulp Duplicates																					
632301	Drill Core	2.96	0.001	0.003	<0.02	0.24	<2	0.006	<0.001	0.04	0.98	<0.02	<0.01	<0.001	<0.01	<0.01	14.31	0.44	0.002	0.16	1.00
REP 632301	QC		0.001	0.003	<0.02	0.24	<2	0.006	<0.001	0.04	0.98	<0.02	<0.01	<0.001	<0.01	<0.01	14.22	0.44	0.002	0.16	1.00
REP 632353	QC		0.006	0.010	0.38	0.41	5	0.011	<0.001	<0.01	0.65	<0.02	<0.01	0.002	<0.01	<0.01	7.66	1.12	0.004	0.10	0.76
Core Reject Duplicates																					
632318	Drill Core	2.08	<0.001	<0.001	<0.02	0.01	<2	0.001	<0.001	0.08	0.33	<0.02	0.02	<0.001	<0.01	<0.01	35.05	0.04	<0.001	0.14	0.23
DUP 632318	QC		<0.001	<0.001	<0.02	0.01	<2	0.001	<0.001	0.08	0.35	<0.02	0.02	<0.001	<0.01	<0.01	35.17	0.04	<0.001	0.14	0.23
632353	Drill Core	0.80	0.005	0.010	0.37	0.41	5	0.011	<0.001	<0.01	0.64	<0.02	<0.01	0.002	<0.01	<0.01	7.54	1.10	0.004	0.10	0.75
DUP 632353	QC		0.005	0.011	0.38	0.43	5	0.011	<0.001	<0.01	0.64	<0.02	<0.01	0.002	<0.01	<0.01	7.50	1.11	0.004	0.10	0.74
Reference Materials																					
STD OREAS131A	Standard		<0.001	0.032	1.78	2.89	32	0.002	0.002	0.18	5.84	<0.02	<0.01	0.008	<0.01	<0.01	5.36	0.06	0.003	3.20	4.68
STD OREAS131A	Standard		<0.001	0.031	1.75	2.84	31	0.002	0.002	0.17	5.77	<0.02	<0.01	0.008	<0.01	<0.01	5.27	0.06	<0.001	3.15	4.61
STD OREAS131A	Standard		<0.001	0.033	1.76	2.91	31	0.003	0.002	0.17	5.92	<0.02	<0.01	0.008	<0.01	<0.01	5.39	0.06	0.002	3.19	4.73
STD R4T	Standard		0.064	0.515	1.60	3.48	90	0.359	0.041	0.09	24.49	<0.02	0.02	0.019	0.02	<0.01	2.24	0.05	0.019	1.45	4.05
STD R4T	Standard		0.063	0.510	1.60	3.45	99	0.356	0.040	0.09	24.23	<0.02	0.02	0.018	<0.01	<0.01	2.18	0.05	0.018	1.41	3.77
STD R4T	Standard		0.064	0.514	1.59	3.47	88	0.358	0.041	0.09	24.32	<0.02	0.02	0.019	0.01	<0.01	2.23	0.04	0.019	1.44	4.05
STD SU-1B	Standard		<0.001	1.179	<0.02	0.02	7	1.993	0.066	0.07	25.45	<0.02	0.03	<0.001	<0.01	<0.01	2.26	0.07	0.032	1.83	4.47
STD SU-1B	Standard		<0.001	1.184	<0.02	0.03	7	2.003	0.066	0.07	25.54	<0.02	0.03	<0.001	<0.01	<0.01	2.25	0.07	0.031	1.82	4.46
STD SU-1B	Standard		<0.001	1.231	<0.02	0.03	6	2.010	0.068	0.07	25.61	<0.02	0.03	<0.001	<0.01	<0.01	2.29	0.06	0.033	1.83	4.52
STD R4T Expected			0.062	0.502	1.518	3.376	86	0.339	0.039	0.086	24.07	0.0087	0.0185	0.018	0.0138	0.0018	2.166	0.045	0.018	1.384	3.897
STD OREAS131A Expected			0.001	0.0322	1.72	2.83	30.9	0.0027	0.0023	0.1722	5.8166	0.0082	0.0028	0.0081	0.0047	0.001	5.286	0.0536	0.0025	3.1182	4.6057
STD SU-1B Expected			0.0004	1.185	0.0058	0.0235	6.4	1.97	0.0672	0.0703	25.54	0.00025	0.03	0.0003	0.00002	0.0003	2.21	0.06	0.032	1.79	4.39
BLK	Blank		<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	<0.01	<0.01	<0.02	<0.01	<0.001	<0.01	<0.01	<0.01	<0.01	<0.001	<0.01	<0.01
BLK	Blank		<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	<0.01	<0.01	<0.02	<0.01	<0.001	<0.01	<0.01	<0.01	<0.01	<0.001	<0.01	<0.01
BLK	Blank		<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	<0.01	<0.01	<0.02	<0.01	<0.001	<0.01	<0.01	<0.01	<0.01	<0.001	<0.01	<0.01
Prep Wash																					
G1	Prep Blank		<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	0.07	2.42	<0.02	0.08	<0.001	<0.01	<0.01	2.38	0.08	<0.001	0.62	7.53
G1	Prep Blank		<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	0.07	2.34	<0.02	0.08	<0.001	<0.01	<0.01	2.37	0.08	<0.001	0.58	7.55



Acme Analytical Laboratories (Vancouver) Ltd.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: Selwyn Resources Ltd.

Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: November 19, 2010

Page: 1 of 1 **Part** 2

QUALITY CONTROL REPORT

WHI10000644.2

Method		7TD	7TD	7TD	7TD	G8SG
Analyte		Na	K	W	S	SG
Unit		%	%	%	%	%
MDL		0.01	0.01	0.01	0.05	0
Pulp Duplicates						
632301	Drill Core	<0.01	0.52	<0.01	1.17	2.46
REP 632301	QC	<0.01	0.51	<0.01	1.18	
REP 632353	QC	<0.01	0.44	<0.01	0.86	
Core Reject Duplicates						
632318	Drill Core	<0.01	0.11	<0.01	0.35	2.59
DUP 632318	QC	<0.01	0.11	<0.01	0.33	2.57
632353	Drill Core	<0.01	0.43	<0.01	0.84	2.41
DUP 632353	QC	<0.01	0.43	<0.01	0.84	2.41
Reference Materials						
STD OREAS131A	Standard	0.16	3.31	<0.01	4.80	
STD OREAS131A	Standard	0.15	3.40	<0.01	4.63	
STD OREAS131A	Standard	0.16	3.26	<0.01	4.85	
STD R4T	Standard	0.94	1.18	<0.01	12.26	
STD R4T	Standard	0.92	1.16	<0.01	12.48	
STD R4T	Standard	0.93	1.20	<0.01	12.21	
STD SU-1B	Standard	1.78	0.62	<0.01	8.45	
STD SU-1B	Standard	1.73	0.61	<0.01	9.19	
STD SU-1B	Standard	1.72	0.63	<0.01	8.51	
STD R4T Expected		0.9	1.153	0.00016	12.9903	
STD OREAS131A Expected		0.1501	3.1584	0.0005	4.8	
STD SU-1B Expected		1.662	0.6	0.0007	8.76	
BLK	Blank	<0.01	<0.01	<0.01	<0.05	
BLK	Blank	<0.01	<0.01	<0.01	<0.05	
BLK	Blank	<0.01	<0.01	<0.01	<0.05	
Prep Wash						
G1	Prep Blank	2.81	2.69	<0.01	<0.05	2.69
G1	Prep Blank	2.82	3.05	<0.01	<0.05	2.67



1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: Selwyn Resources Ltd.

Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Submitted By: Jason K. Dunning

Receiving Lab: Canada-Whitehorse

Received: November 08, 2010

Report Date: November 17, 2010

Page: 1 of 4

CERTIFICATE OF ANALYSIS

WHI10000644.1

CLIENT JOB INFORMATION

Project: Selwyn Project
Shipment ID:
P.O. Number 1710-DON-426
Number of Samples: 63

SAMPLE DISPOSAL

STOR-PLP Store After 90 days Invoice for Storage
STOR-RJT Store After 90 days Invoice for Storage

Acme does not accept responsibility for samples left at the laboratory after 90 days without prior written instructions for sample storage or return.

Invoice To: Selwyn Resources Ltd.
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6
Canada

CC:

SAMPLE PREPARATION AND ANALYTICAL PROCEDURES

Method Code	Number of Samples	Code Description	Test Wgt (g)	Report Status	Lab
R200-250	61	Crush split and pulverize 250g drill core to 200 mesh			WHI
7TD2	63	4 Acid digestion ICP-ES analysis.	0.5	Completed	VAN
G8SG	63	Specific Gravity on Pulp		Completed	VAN

ADDITIONAL COMMENTS



This report supersedes all previous preliminary and final reports with this file number dated prior to the date on this certificate. Signature indicates final approval; preliminary reports are unsigned and should be used for reference only.
All results are considered the confidential property of the client. Acme assumes the liabilities for actual cost of analysis only.
"*" asterisk indicates that an analytical result could not be provided due to unusually high levels of interference from other elements.



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: November 17, 2010

Page: 2 of 4 Part 1

CERTIFICATE OF ANALYSIS

WHI10000644.1

	Method Analyte Unit MDL	WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD
		Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg	Al
		kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%	%
		0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01	0.01
632301	Drill Core	2.96	0.001	0.003	<0.02	0.24	<2	0.006	<0.001	0.04	0.98	<0.02	<0.01	<0.001	<0.01	<0.01	14.31	0.44	0.002	0.16	1.00
632302	Drill Core	2.18	0.002	0.004	0.05	0.33	<2	0.011	<0.001	<0.01	1.77	<0.02	<0.01	0.001	<0.01	<0.01	2.15	0.75	0.004	0.19	1.95
632303	Drill Core	1.45	0.005	0.004	0.42	0.05	<2	0.012	<0.001	<0.01	2.09	<0.02	<0.01	<0.001	<0.01	<0.01	1.49	0.10	0.003	0.18	1.83
632304	Drill Core	1.00	0.002	0.013	1.33	2.20	<2	0.004	<0.001	0.03	7.09	<0.02	<0.01	0.020	<0.01	<0.01	11.78	0.02	0.001	0.06	0.44
632305	Drill Core	1.13	<0.001	0.008	5.30	6.54	<2	0.003	<0.001	0.01	4.59	<0.02	<0.01	0.062	<0.01	<0.01	1.38	0.03	0.001	0.07	0.61
632306	Drill Core	0.91	<0.001	0.001	0.07	0.32	<2	0.002	<0.001	0.06	1.01	<0.02	0.02	0.001	<0.01	<0.01	27.05	0.02	<0.001	0.09	0.25
632307	Drill Core	1.88	0.004	0.009	1.24	8.57	<2	0.009	<0.001	0.02	5.86	<0.02	<0.01	0.031	<0.01	<0.01	5.98	0.05	0.002	0.12	1.23
632308	Drill Core	2.65	0.003	0.007	2.05	6.96	<2	0.008	<0.001	0.01	4.76	<0.02	<0.01	0.024	<0.01	<0.01	0.44	0.04	0.002	0.08	0.93
632309	Drill Core	2.15	0.003	0.006	1.06	7.69	<2	0.007	<0.001	0.02	3.65	<0.02	<0.01	0.018	<0.01	<0.01	3.67	0.05	0.001	0.08	0.81
632310	Drill Core	0.30	<0.001	0.002	1.15	2.39	<2	0.002	<0.001	0.07	1.36	<0.02	0.01	0.010	<0.01	<0.01	20.46	0.03	0.001	0.08	0.29
632311	Drill Core	0.39	<0.001	0.002	1.28	2.15	<2	0.002	<0.001	0.06	0.86	<0.02	<0.01	0.009	<0.01	<0.01	19.11	0.03	<0.001	0.08	0.28
632312	Drill Core	2.10	0.001	0.002	0.04	0.97	<2	0.003	<0.001	<0.01	1.68	<0.02	<0.01	0.003	<0.01	<0.01	1.83	0.04	<0.001	0.05	0.49
632313	Drill Core	2.08	0.002	0.003	1.24	3.84	<2	0.004	<0.001	<0.01	1.69	<0.02	<0.01	0.012	<0.01	<0.01	4.09	0.05	<0.001	0.06	0.67
632314	Drill Core	2.35	0.001	0.001	0.03	0.47	<2	0.005	<0.001	<0.01	0.79	<0.02	<0.01	0.001	<0.01	<0.01	3.05	0.04	0.001	0.05	0.57
632315	Drill Core	1.88	0.007	0.003	0.13	0.96	<2	0.012	<0.001	<0.01	1.82	<0.02	<0.01	0.003	<0.01	<0.01	1.68	0.05	0.002	0.13	1.63
632316	Drill Core	2.10	0.007	0.012	1.20	7.59	<2	0.012	<0.001	0.03	5.15	<0.02	<0.01	0.021	<0.01	<0.01	4.43	0.05	0.002	0.12	1.48
632317	Drill Core	2.40	<0.001	<0.001	<0.02	0.02	<2	<0.001	<0.001	0.08	0.50	<0.02	0.02	<0.001	<0.01	<0.01	33.89	0.03	<0.001	0.13	0.15
632318	Drill Core	2.08	<0.001	<0.001	<0.02	0.01	<2	0.001	<0.001	0.08	0.33	<0.02	0.02	<0.001	<0.01	<0.01	35.05	0.04	<0.001	0.14	0.23
632319	Drill Core	3.14	<0.001	<0.001	<0.02	0.01	<2	<0.001	<0.001	0.08	2.87	<0.02	0.02	<0.001	<0.01	<0.01	31.70	0.03	<0.001	0.14	0.17
632320	Rock	0.39	<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	0.01	0.12	<0.02	0.01	<0.001	<0.01	<0.01	20.73	0.03	<0.001	10.92	0.13
632321	Drill Core	1.52	<0.001	<0.001	<0.02	0.01	<2	0.001	<0.001	0.07	0.28	<0.02	0.02	<0.001	<0.01	<0.01	34.00	0.03	<0.001	0.10	0.16
632322	Drill Core	1.56	<0.001	<0.001	<0.02	<0.01	<2	0.002	<0.001	0.03	0.44	<0.02	<0.01	<0.001	<0.01	<0.01	18.59	0.05	<0.001	0.07	0.30
632323	Drill Core	0.64	<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	0.09	0.35	<0.02	0.02	<0.001	<0.01	<0.01	34.82	0.04	<0.001	0.19	0.14
632324	Drill Core	1.16	0.001	0.005	0.80	2.72	<2	0.007	<0.001	0.02	14.80	<0.02	<0.01	0.007	<0.01	<0.01	3.63	0.12	0.002	0.10	0.85
632325	Drill Core	2.84	0.001	0.003	1.79	4.58	<2	0.006	<0.001	0.02	2.15	<0.02	<0.01	0.012	<0.01	<0.01	3.72	0.08	0.001	0.11	0.90
632326	Drill Core	3.03	0.001	0.002	0.74	3.84	<2	0.002	<0.001	0.05	2.24	<0.02	0.01	0.011	<0.01	<0.01	27.63	0.04	0.001	0.09	0.38
632327	Drill Core	1.17	0.002	0.003	0.32	1.40	<2	0.007	<0.001	0.02	2.11	<0.02	<0.01	0.004	<0.01	<0.01	8.27	0.09	0.001	0.11	0.87
632328	Drill Core	1.07	0.001	0.002	1.45	2.60	<2	0.005	<0.001	0.02	4.58	<0.02	<0.01	0.007	<0.01	<0.01	4.34	0.04	0.002	0.10	0.69
632329	Drill Core	1.47	<0.001	0.005	3.80	28.02	5	0.002	<0.001	0.02	1.26	<0.02	<0.01	0.069	<0.01	<0.01	12.39	0.04	<0.001	0.04	0.23
632330	Rock Pulp	0.02	0.002	0.813	0.92	1.26	216	0.002	0.002	0.23	2.58	<0.02	0.01	0.008	0.02	<0.01	1.92	0.01	0.003	0.12	1.25



Acme Analytical Laboratories (Vancouver) Ltd.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client:

Selwyn Resources Ltd.

Suite 700 - 509 Richards Street

Vancouver BC V6B 2Z6 Canada

Project:

Selwyn Project

Report Date:

November 17, 2010

Page:

2 of 4

Part 2

CERTIFICATE OF ANALYSIS

WHI10000644.1

Method	7TD	7TD	7TD	7TD	G8SG
Analyte	Na	K	W	S	SG
Unit	%	%	%	%	
MDL	0.01	0.01	0.01	0.05	0
632301	Drill Core	<0.01	0.52	<0.01	1.17 2.46383
632302	Drill Core	<0.01	1.02	<0.01	2.05 2.38532
632303	Drill Core	<0.01	0.95	<0.01	2.39 2.40765
632304	Drill Core	<0.01	0.24	<0.01	9.72 2.87715
632305	Drill Core	<0.01	0.32	<0.01	8.76 2.8422
632306	Drill Core	<0.01	0.13	<0.01	1.29 2.5307
632307	Drill Core	<0.01	0.67	<0.01	11.01 2.73536
632308	Drill Core	<0.01	0.47	<0.01	9.03 2.6398
632309	Drill Core	<0.01	0.44	<0.01	7.93 2.62602
632310	Drill Core	<0.01	0.14	<0.01	2.78 2.69758
632311	Drill Core	<0.01	0.14	<0.01	2.11 2.67342
632312	Drill Core	<0.01	0.23	<0.01	2.06 2.5079
632313	Drill Core	<0.01	0.36	<0.01	3.82 2.64066
632314	Drill Core	<0.01	0.29	<0.01	0.87 2.44647
632315	Drill Core	<0.01	0.89	<0.01	2.35 2.35205
632316	Drill Core	<0.01	0.88	<0.01	9.69 2.56459
632317	Drill Core	<0.01	0.07	<0.01	0.54 2.61552
632318	Drill Core	<0.01	0.11	<0.01	0.35 2.58961
632319	Drill Core	<0.01	0.08	<0.01	3.24 2.62294
632320	Rock	<0.01	0.02	<0.01	<0.05 2.74658
632321	Drill Core	<0.01	0.07	<0.01	0.39 2.52623
632322	Drill Core	<0.01	0.14	<0.01	0.34 2.55167
632323	Drill Core	<0.01	0.07	<0.01	0.37 2.66275
632324	Drill Core	<0.01	0.46	<0.01	17.88 2.85602
632325	Drill Core	<0.01	0.48	<0.01	4.78 2.57565
632326	Drill Core	<0.01	0.17	<0.01	4.48 2.6419
632327	Drill Core	<0.01	0.47	<0.01	2.96 2.50299
632328	Drill Core	<0.01	0.36	<0.01	6.56 2.65461
632329	Drill Core	<0.01	0.12	<0.01	16.22 3.09773
632330	Rock Pulp	0.57	0.28	<0.01	2.04 I.S.



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: November 17, 2010

Page: 3 of 4 Part 1

CERTIFICATE OF ANALYSIS

WHI10000644.1

	Method Analyte Unit MDL	WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD
		Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg	Al
		kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%	%
		0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01	0.01
632331	Drill Core	1.57	0.002	0.004	2.15	5.57	3	0.006	<0.001	0.03	3.57	<0.02	<0.01	0.014	<0.01	<0.01	11.53	0.06	0.002	0.10	0.70
632332	Drill Core	1.78	0.002	0.004	2.48	9.59	3	0.006	<0.001	0.02	2.39	<0.02	<0.01	0.030	<0.01	<0.01	4.75	0.07	0.002	0.09	0.72
632333	Drill Core	0.82	0.001	0.006	1.41	12.63	4	0.003	<0.001	0.04	1.73	<0.02	0.01	0.027	<0.01	<0.01	20.55	0.03	0.001	0.07	0.35
632334	Drill Core	2.63	<0.001	0.002	0.38	1.84	<2	0.003	<0.001	0.04	0.78	<0.02	0.02	0.004	<0.01	<0.01	31.24	0.07	0.001	0.11	0.47
632335	Drill Core	2.61	<0.001	0.002	0.03	0.08	<2	0.004	<0.001	0.04	0.85	<0.02	0.02	<0.001	<0.01	<0.01	29.34	0.06	0.001	0.13	0.66
632336	Drill Core	1.90	<0.001	0.002	<0.02	0.02	<2	0.003	<0.001	0.04	0.97	<0.02	0.02	<0.001	<0.01	<0.01	30.98	0.04	0.001	0.12	0.53
632337	Drill Core	2.39	0.003	0.004	0.34	1.86	<2	0.008	<0.001	0.02	1.47	<0.02	<0.01	0.004	<0.01	<0.01	6.52	0.08	0.002	0.13	1.17
632338	Drill Core	0.90	0.003	0.011	1.62	9.27	4	0.009	<0.001	<0.01	3.74	<0.02	<0.01	0.023	<0.01	<0.01	1.77	0.05	0.002	0.08	0.74
632339	Drill Core	2.00	0.001	0.002	0.07	0.06	<2	0.005	<0.001	<0.01	1.38	<0.02	<0.01	<0.001	<0.01	<0.01	1.81	0.04	0.001	0.07	0.51
632340	Drill Core	1.05	<0.001	0.002	0.04	0.08	<2	0.003	<0.001	0.05	0.65	<0.02	0.02	<0.001	<0.01	<0.01	31.34	0.05	0.001	0.11	0.53
632341	Drill Core	1.35	<0.001	0.002	0.04	0.09	<2	0.003	<0.001	0.05	0.57	<0.02	0.02	<0.001	<0.01	<0.01	31.54	0.06	0.001	0.11	0.53
632342	Drill Core	2.70	0.002	0.004	0.47	0.71	<2	0.006	<0.001	0.01	0.74	<0.02	<0.01	0.002	<0.01	<0.01	3.81	0.06	0.002	0.08	0.60
632343	Drill Core	1.95	0.003	0.008	0.06	0.65	3	0.009	<0.001	0.04	4.53	<0.02	<0.01	0.002	<0.01	<0.01	11.66	0.37	0.003	0.10	0.64
632344	Drill Core	0.74	0.005	0.006	0.05	4.45	3	0.016	<0.001	<0.01	4.47	<0.02	<0.01	0.015	<0.01	<0.01	1.23	0.26	0.004	0.13	1.01
632345	Drill Core	2.44	0.007	0.019	0.06	0.75	3	0.012	<0.001	0.03	1.90	<0.02	0.01	0.003	<0.01	<0.01	18.95	1.49	0.006	0.11	0.75
632346	Drill Core	1.54	0.006	0.010	0.03	0.22	3	0.009	<0.001	0.05	4.67	<0.02	0.01	<0.001	<0.01	<0.01	21.36	0.12	0.003	0.18	0.58
632347	Drill Core	1.64	0.005	0.007	0.03	0.25	<2	0.007	<0.001	0.05	1.71	<0.02	0.02	0.001	<0.01	<0.01	23.05	0.11	0.002	0.16	0.63
632348	Drill Core	1.54	0.001	0.004	0.12	0.06	2	0.004	<0.001	0.08	1.34	<0.02	0.02	<0.001	<0.01	<0.01	33.86	0.02	<0.001	0.16	0.18
632349	Drill Core	2.34	0.004	0.008	1.24	0.17	9	0.006	<0.001	0.03	4.23	<0.02	<0.01	<0.001	<0.01	<0.01	17.32	0.20	0.002	0.09	0.45
632350	Rock	0.34	<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	0.01	0.16	<0.02	<0.01	<0.001	<0.01	<0.01	21.41	0.04	<0.001	11.42	0.18
632351	Drill Core	1.19	0.004	0.016	0.12	0.59	3	0.008	<0.001	0.03	1.71	<0.02	0.01	0.002	<0.01	<0.01	21.77	0.31	0.004	0.13	0.70
632352	Drill Core	1.64	0.003	0.009	0.08	0.41	3	0.007	<0.001	0.02	1.11	<0.02	<0.01	0.002	<0.01	<0.01	13.30	0.21	0.003	0.08	0.45
632353	Drill Core	0.80	0.005	0.010	0.37	0.41	5	0.011	<0.001	<0.01	0.64	<0.02	<0.01	0.002	<0.01	<0.01	7.54	1.10	0.004	0.10	0.75
632354	Drill Core	1.15	0.005	0.055	0.43	0.93	7	0.013	<0.001	<0.01	7.79	<0.02	<0.01	0.003	<0.01	<0.01	4.49	0.23	0.005	0.11	0.86
632355	Drill Core	2.16	0.008	0.017	0.10	0.46	3	0.016	<0.001	0.01	1.03	<0.02	<0.01	0.002	<0.01	<0.01	6.52	0.23	0.005	0.15	1.20
632356	Drill Core	2.67	0.011	0.016	0.06	0.46	5	0.021	<0.001	<0.01	1.35	<0.02	<0.01	0.002	<0.01	<0.01	1.68	0.11	0.006	0.17	1.42
632357	Drill Core	1.65	0.004	0.028	0.15	0.31	5	0.026	<0.001	<0.01	4.45	<0.02	<0.01	0.001	<0.01	<0.01	7.17	2.25	0.016	0.25	2.10
632358	Drill Core	2.10	<0.001	0.003	<0.02	<0.01	<2	0.004	<0.001	0.04	1.72	<0.02	0.02	<0.001	<0.01	<0.01	21.44	0.38	0.004	0.36	2.65
632359	Drill Core	2.69	<0.001	0.002	<0.02	<0.01	<2	0.002	<0.001	0.04	1.46	<0.02	0.02	<0.001	<0.01	<0.01	26.98	0.02	0.003	0.40	2.59
632360	Rock Pulp	0.02	<0.001	0.497	1.51	4.34	29	0.001	0.001	0.70	5.33	<0.02	0.01	0.027	<0.01	<0.01	4.25	0.05	0.004	1.56	4.47



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**

Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: November 17, 2010

Page: 3 of 4 Part 2

CERTIFICATE OF ANALYSIS

WHI10000644.1

Method	7TD	7TD	7TD	7TD	G8SG
Analyte	Na	K	W	S	SG
Unit	%	%	%	%	
MDL	0.01	0.01	0.01	0.05	0
632331	Drill Core	<0.01	0.39	<0.01	7.74 2.72808
632332	Drill Core	<0.01	0.39	<0.01	8.09 2.72163
632333	Drill Core	<0.01	0.18	<0.01	8.79 2.85125
632334	Drill Core	<0.01	0.23	<0.01	1.93 2.53939
632335	Drill Core	<0.01	0.33	<0.01	1.09 2.46672
632336	Drill Core	<0.01	0.26	<0.01	1.17 2.54974
632337	Drill Core	<0.01	0.71	<0.01	2.64 2.41791
632338	Drill Core	<0.01	0.43	<0.01	9.36 2.65126
632339	Drill Core	<0.01	0.28	<0.01	1.38 2.52041
632340	Drill Core	<0.01	0.27	<0.01	0.79 2.45692
632341	Drill Core	<0.01	0.27	<0.01	0.70 2.55537
632342	Drill Core	<0.01	0.33	<0.01	1.01 2.53554
632343	Drill Core	<0.01	0.37	<0.01	5.71 2.55745
632344	Drill Core	<0.01	0.55	<0.01	7.27 2.53843
632345	Drill Core	<0.01	0.38	<0.01	2.59 2.38197
632346	Drill Core	<0.01	0.30	<0.01	5.69 2.5975
632347	Drill Core	<0.01	0.32	<0.01	2.14 2.5034
632348	Drill Core	<0.01	0.09	<0.01	1.67 2.55975
632349	Drill Core	<0.01	0.23	<0.01	5.27 2.64828
632350	Rock	0.01	0.04	<0.01	<0.05 2.72396
632351	Drill Core	<0.01	0.36	<0.01	2.26 2.47846
632352	Drill Core	<0.01	0.25	<0.01	1.45 2.49634
632353	Drill Core	<0.01	0.43	<0.01	0.84 2.41181
632354	Drill Core	<0.01	0.49	<0.01	9.67 2.55197
632355	Drill Core	<0.01	0.68	<0.01	1.33 2.34069
632356	Drill Core	<0.01	0.81	<0.01	1.60 2.32133
632357	Drill Core	<0.01	1.23	<0.01	5.19 2.36411
632358	Drill Core	<0.01	1.40	<0.01	1.94 2.53538
632359	Drill Core	<0.01	1.39	<0.01	1.59 2.61152
632360	Rock Pulp	0.09	3.30	<0.01	5.00 N.A.



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: November 17, 2010

Page: 4 of 4 **Part** 1

CERTIFICATE OF ANALYSIS

WHI10000644.1

	Method	WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD
	Analyte	Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg
	Unit	kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%
	MDL	0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01
632361	Drill Core	2.34	0.002	0.004	<0.02	<0.01	<2	0.008	<0.001	0.04	2.68	<0.02	0.01	<0.001	<0.01	<0.01	19.82	0.02	0.004	0.47
632362	Drill Core	2.42	0.005	0.006	<0.02	<0.01	<2	0.012	<0.001	0.01	3.46	<0.02	0.03	<0.001	<0.01	<0.01	22.44	8.21	0.007	0.19
632363	Drill Core	1.81	0.011	0.011	<0.02	0.09	7	0.031	0.001	<0.01	2.92	<0.02	<0.01	<0.001	<0.01	<0.01	1.45	0.27	0.017	0.52



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: November 17, 2010

Page: 4 of 4 **Part** 2

CERTIFICATE OF ANALYSIS

WHI10000644.1

	Method	7TD	7TD	7TD	7TD	G8SG
	Analyte	Na	K	W	S	SG
	Unit	%	%	%	%	
	MDL	0.01	0.01	0.01	0.05	0
632361	Drill Core	<0.01	1.74	<0.01	3.00	2.58165
632362	Drill Core	0.02	0.90	<0.01	3.97	2.64468
632363	Drill Core	<0.01	2.94	<0.01	3.28	2.23133



Acme Analytical Laboratories (Vancouver) Ltd.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: Selwyn Resources Ltd.

Suite 700 - 509 Richards Street

Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: November 17, 2010

Page: 1 of 1 Part 1

QUALITY CONTROL REPORT

WHI10000644.1

	Method Analyte Unit MDL	WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD
		Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg	Al
		kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%	%
		0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01	0.01
Pulp Duplicates																					
632301	Drill Core	2.96	0.001	0.003	<0.02	0.24	<2	0.006	<0.001	0.04	0.98	<0.02	<0.01	<0.001	<0.01	<0.01	14.31	0.44	0.002	0.16	1.00
REP 632301	QC		0.001	0.003	<0.02	0.24	<2	0.006	<0.001	0.04	0.98	<0.02	<0.01	<0.001	<0.01	<0.01	14.22	0.44	0.002	0.16	1.00
REP 632353	QC		0.006	0.010	0.38	0.41	5	0.011	<0.001	<0.01	0.65	<0.02	<0.01	0.002	<0.01	<0.01	7.66	1.12	0.004	0.10	0.76
Core Reject Duplicates																					
632318	Drill Core	2.08	<0.001	<0.001	<0.02	0.01	<2	0.001	<0.001	0.08	0.33	<0.02	0.02	<0.001	<0.01	<0.01	35.05	0.04	<0.001	0.14	0.23
DUP 632318	QC		<0.001	<0.001	<0.02	0.01	<2	0.001	<0.001	0.08	0.35	<0.02	0.02	<0.001	<0.01	<0.01	35.17	0.04	<0.001	0.14	0.23
632353	Drill Core	0.80	0.005	0.010	0.37	0.41	5	0.011	<0.001	<0.01	0.64	<0.02	<0.01	0.002	<0.01	<0.01	7.54	1.10	0.004	0.10	0.75
DUP 632353	QC		0.005	0.011	0.38	0.43	5	0.011	<0.001	<0.01	0.64	<0.02	<0.01	0.002	<0.01	<0.01	7.50	1.11	0.004	0.10	0.74
Reference Materials																					
STD OREAS131A	Standard		<0.001	0.032	1.78	2.89	32	0.002	0.002	0.18	5.84	<0.02	<0.01	0.008	<0.01	<0.01	5.36	0.06	0.003	3.20	4.68
STD OREAS131A	Standard		<0.001	0.031	1.75	2.84	31	0.002	0.002	0.17	5.77	<0.02	<0.01	0.008	<0.01	<0.01	5.27	0.06	<0.001	3.15	4.61
STD OREAS131A	Standard		<0.001	0.033	1.76	2.91	31	0.003	0.002	0.17	5.92	<0.02	<0.01	0.008	<0.01	<0.01	5.39	0.06	0.002	3.19	4.73
STD R4T	Standard		0.064	0.515	1.60	3.48	90	0.359	0.041	0.09	24.49	<0.02	0.02	0.019	0.02	<0.01	2.24	0.05	0.019	1.45	4.05
STD R4T	Standard		0.063	0.510	1.60	3.45	99	0.356	0.040	0.09	24.23	<0.02	0.02	0.018	<0.01	<0.01	2.18	0.05	0.018	1.41	3.77
STD R4T	Standard		0.064	0.514	1.59	3.47	88	0.358	0.041	0.09	24.32	<0.02	0.02	0.019	0.01	<0.01	2.23	0.04	0.019	1.44	4.05
STD SU-1B	Standard		<0.001	1.179	<0.02	0.02	7	1.993	0.066	0.07	25.45	<0.02	0.03	<0.001	<0.01	<0.01	2.26	0.07	0.032	1.83	4.47
STD SU-1B	Standard		<0.001	1.184	<0.02	0.03	7	2.003	0.066	0.07	25.54	<0.02	0.03	<0.001	<0.01	<0.01	2.25	0.07	0.031	1.82	4.46
STD SU-1B	Standard		<0.001	1.231	<0.02	0.03	6	2.010	0.068	0.07	25.61	<0.02	0.03	<0.001	<0.01	<0.01	2.29	0.06	0.033	1.83	4.52
STD R4T Expected			0.062	0.502	1.518	3.376	86	0.339	0.039	0.086	24.07	0.0087	0.0185	0.018	0.0138	0.0018	2.166	0.045	0.018	1.384	3.897
STD OREAS131A Expected			0.001	0.0322	1.72	2.83	30.9	0.0027	0.0023	0.1722	5.8166	0.0082	0.0028	0.0081	0.0047	0.001	5.286	0.0536	0.0025	3.1182	4.6057
STD SU-1B Expected			0.0004	1.185	0.0058	0.0235	6.4	1.97	0.0672	0.0703	25.54	0.00025	0.03	0.0003	0.00002	0.0003	2.21	0.06	0.032	1.79	4.39
BLK	Blank		<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	<0.01	<0.01	<0.02	<0.01	<0.001	<0.01	<0.01	<0.01	<0.01	<0.001	<0.01	
BLK	Blank		<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	<0.01	<0.01	<0.02	<0.01	<0.001	<0.01	<0.01	<0.01	<0.01	<0.001	<0.01	
BLK	Blank		<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	<0.01	<0.01	<0.02	<0.01	<0.001	<0.01	<0.01	<0.01	<0.01	<0.001	<0.01	
Prep Wash																					
G1	Prep Blank		<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	0.07	2.42	<0.02	0.08	<0.001	<0.01	<0.01	2.38	0.08	<0.001	0.62	7.53
G1	Prep Blank		<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	0.07	2.34	<0.02	0.08	<0.001	<0.01	<0.01	2.37	0.08	<0.001	0.58	7.55



Acme Analytical Laboratories (Vancouver) Ltd.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: **Selwyn Resources Ltd.**

Suite 700 - 509 Richards Street

Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: November 17, 2010

Page: 1 of 1 **Part** 2

QUALITY CONTROL REPORT

WHI10000644.1

Method		7TD	7TD	7TD	7TD	G8SG
Analyte		Na	K	W	S	SG
Unit		%	%	%	%	%
MDL		0.01	0.01	0.01	0.05	0
Pulp Duplicates						
632301	Drill Core	<0.01	0.52	<0.01	1.17	2.46383
REP 632301	QC	<0.01	0.51	<0.01	1.18	
REP 632353	QC	<0.01	0.44	<0.01	0.86	
Core Reject Duplicates						
632318	Drill Core	<0.01	0.11	<0.01	0.35	2.58961
DUP 632318	QC	<0.01	0.11	<0.01	0.33	2.57416
632353	Drill Core	<0.01	0.43	<0.01	0.84	2.41181
DUP 632353	QC	<0.01	0.43	<0.01	0.84	2.40811
Reference Materials						
STD OREAS131A	Standard	0.16	3.31	<0.01	4.80	
STD OREAS131A	Standard	0.15	3.40	<0.01	4.63	
STD OREAS131A	Standard	0.16	3.26	<0.01	4.85	
STD R4T	Standard	0.94	1.18	<0.01	12.26	
STD R4T	Standard	0.92	1.16	<0.01	12.48	
STD R4T	Standard	0.93	1.20	<0.01	12.21	
STD SU-1B	Standard	1.78	0.62	<0.01	8.45	
STD SU-1B	Standard	1.73	0.61	<0.01	9.19	
STD SU-1B	Standard	1.72	0.63	<0.01	8.51	
STD R4T Expected		0.9	1.153	0.00016	12.9903	
STD OREAS131A Expected		0.1501	3.1584	0.0005	4.8	
STD SU-1B Expected		1.662	0.6	0.0007	8.76	
BLK	Blank	<0.01	<0.01	<0.01	<0.05	
BLK	Blank	<0.01	<0.01	<0.01	<0.05	
BLK	Blank	<0.01	<0.01	<0.01	<0.05	
Prep Wash						
G1	Prep Blank	2.81	2.69	<0.01	<0.05	2.69127
G1	Prep Blank	2.82	3.05	<0.01	<0.05	2.66583



1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**

Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Submitted By: Jason K. Dunning

Receiving Lab: Canada-Whitehorse

Received: August 30, 2010

Report Date: September 10, 2010

Page: 1 of 3

CERTIFICATE OF ANALYSIS

WHI10000348.1

CLIENT JOB INFORMATION

Project: Selwyn Project
Shipment ID:
P.O. Number: 1710-DON-199
Number of Samples: 35

SAMPLE PREPARATION AND ANALYTICAL PROCEDURES

Method Code	Number of Samples	Code Description	Test Wgt (g)	Report Status	Lab
R200-250	34	Crush split and pulverize 250g drill core to 200 mesh			WHI
7TD2	35	4 Acid digestion ICP-ES analysis.	0.5	Completed	VAN

SAMPLE DISPOSAL

STOR-PLP Store After 90 days Invoice for Storage
STOR-RJT Store After 90 days Invoice for Storage

ADDITIONAL COMMENTS

Acme does not accept responsibility for samples left at the laboratory after 90 days without prior written instructions for sample storage or return.

Invoice To: Selwyn Resources Ltd.
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6
Canada

CC:



This report supersedes all previous preliminary and final reports with this file number dated prior to the date on this certificate. Signature indicates final approval; preliminary reports are unsigned and should be used for reference only.

All results are considered the confidential property of the client. Acme assumes the liabilities for actual cost of analysis only.

“**” asterisk indicates that an analytical result could not be provided due to unusually high levels of interference from other elements.



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: September 10, 2010

Page: 2 of 3 Part 1

CERTIFICATE OF ANALYSIS

WHI10000348.1

	Method Analyte Unit MDL	WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD
		Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg	Al
		kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%	%
		0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01	0.01
631951	Drill Core	1.28	0.004	0.010	<0.02	0.73	2	0.012	<0.001	<0.01	1.59	<0.02	<0.01	0.002	<0.01	<0.01	0.92	0.22	0.003	0.28	2.21
631952	Drill Core	1.57	<0.001	0.002	<0.02	0.20	<2	0.003	<0.001	<0.01	0.61	<0.02	<0.01	<0.001	<0.01	<0.01	0.62	0.05	0.003	0.09	0.68
631953	Drill Core	1.05	0.001	0.005	0.02	0.14	<2	0.004	<0.001	<0.01	1.11	<0.02	<0.01	<0.001	<0.01	<0.01	2.32	0.42	0.004	0.12	0.97
631954	Drill Core	1.98	0.002	0.003	0.49	1.03	<2	0.004	<0.001	0.03	1.43	<0.02	<0.01	0.003	<0.01	<0.01	9.19	0.12	0.002	0.08	0.57
631955	Drill Core	2.35	0.004	0.016	1.42	10.02	3	0.009	<0.001	0.05	6.38	<0.02	<0.01	0.028	<0.01	<0.01	8.19	0.14	0.002	0.09	0.87
631956	Drill Core	1.83	<0.001	0.001	0.62	1.51	<2	<0.001	<0.001	0.07	0.84	<0.02	0.02	0.005	<0.01	<0.01	32.00	0.04	<0.001	0.10	0.10
631957	Drill Core	2.03	<0.001	<0.001	0.33	1.39	<2	<0.001	<0.001	0.08	0.86	<0.02	0.02	0.004	<0.01	<0.01	31.49	0.05	<0.001	0.10	0.11
631958	Drill Core	0.68	<0.001	0.001	0.13	0.84	<2	0.003	<0.001	0.03	0.65	<0.02	<0.01	0.002	<0.01	<0.01	13.00	0.09	0.001	0.09	0.56
631959	Drill Core	2.03	<0.001	<0.001	0.32	1.17	<2	0.001	<0.001	0.07	0.47	<0.02	0.02	0.004	<0.01	<0.01	31.55	0.04	<0.001	0.08	0.13
631960	Drill Core	1.23	<0.001	0.002	0.55	1.74	<2	0.003	<0.001	0.05	0.99	<0.02	0.01	0.005	<0.01	<0.01	23.29	0.07	0.001	0.10	0.42
631961	Drill Core	1.22	<0.001	0.002	0.34	2.19	<2	0.004	<0.001	0.05	1.38	<0.02	0.01	0.006	<0.01	<0.01	21.40	0.08	0.001	0.11	0.64
631962	Drill Core	1.11	0.001	0.003	1.99	3.95	<2	0.006	<0.001	0.02	2.64	<0.02	<0.01	0.011	<0.01	<0.01	7.26	0.08	0.002	0.11	0.88
631963	Drill Core	1.13	<0.001	0.001	0.61	2.15	<2	0.002	<0.001	0.04	1.27	<0.02	0.01	0.006	<0.01	<0.01	24.54	0.03	<0.001	0.07	0.27
631964	Drill Core	0.88	0.002	0.005	1.26	8.18	3	0.004	<0.001	0.05	3.63	<0.02	0.01	0.023	<0.01	<0.01	17.87	0.05	0.001	0.09	0.55
631965	Drill Core	1.74	0.002	0.004	1.61	4.22	<2	0.005	<0.001	0.05	3.14	<0.02	0.01	0.011	<0.01	<0.01	21.30	0.05	0.001	0.11	0.63
631966	Drill Core	0.87	0.002	0.005	1.25	6.41	<2	0.005	<0.001	0.03	2.37	<0.02	<0.01	0.018	<0.01	<0.01	7.27	0.05	0.002	0.08	0.56
631967	Drill Core	2.07	0.001	0.004	0.38	0.77	<2	0.004	<0.001	0.04	1.47	<0.02	0.01	0.002	<0.01	<0.01	18.05	0.06	0.001	0.11	0.58
631968	Drill Core	1.25	0.002	0.004	0.13	0.49	<2	0.006	<0.001	0.01	1.13	<0.02	<0.01	0.001	<0.01	<0.01	2.81	0.07	0.003	0.09	0.71
631969	Drill Core	1.81	0.001	0.004	0.08	0.92	<2	0.004	<0.001	0.02	0.95	<0.02	<0.01	0.002	<0.01	<0.01	8.37	0.06	0.001	0.06	0.42
631970	Drill Core	0.47	<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	0.02	0.19	<0.02	<0.01	<0.001	<0.01	<0.01	20.49	0.03	<0.001	10.50	0.14
631971	Drill Core	1.54	0.001	0.004	0.03	0.50	<2	0.004	<0.001	0.01	0.66	<0.02	<0.01	0.001	<0.01	<0.01	6.12	0.04	0.001	0.07	0.50
631972	Drill Core	1.10	0.002	0.005	1.77	0.78	3	0.007	<0.001	0.03	1.01	<0.02	0.01	0.002	<0.01	<0.01	16.28	0.08	0.002	0.13	0.86
631973	Drill Core	2.66	0.004	0.011	0.70	1.87	2	0.011	<0.001	0.02	3.62	<0.02	<0.01	0.004	<0.01	<0.01	5.96	0.46	0.003	0.11	0.90
631974	Drill Core	1.56	0.003	0.012	0.16	0.87	<2	0.007	<0.001	0.06	0.69	<0.02	0.02	0.003	<0.01	<0.01	22.95	0.82	0.003	0.11	0.67
631975	Drill Core	1.90	0.011	0.029	0.16	0.48	2	0.014	<0.001	0.02	1.38	<0.02	0.01	0.002	<0.01	<0.01	10.48	1.08	0.006	0.15	1.13
631976	Drill Core	2.10	0.005	0.010	0.20	2.11	3	0.011	<0.001	0.02	0.96	<0.02	<0.01	0.006	<0.01	<0.01	10.99	0.38	0.004	0.12	0.86
631977	Drill Core	2.24	0.002	0.006	0.20	0.50	<2	0.005	<0.001	0.03	0.40	<0.02	0.01	0.001	<0.01	<0.01	20.09	0.27	0.002	0.07	0.39
631978	Drill Core	3.10	0.008	0.014	0.38	1.73	3	0.015	<0.001	0.02	0.98	<0.02	<0.01	0.004	<0.01	<0.01	8.59	0.32	0.006	0.14	1.17
631979	Drill Core	1.55	0.008	0.020	0.57	1.60	5	0.016	<0.001	<0.01	1.20	<0.02	<0.01	0.005	<0.01	<0.01	3.03	0.25	0.005	0.14	1.22
631980	Core Pulp	0.06	0.002	0.831	0.93	1.35	216	0.002	0.002	0.25	2.79	<0.02	0.01	0.009	0.04	<0.01	2.00	0.01	0.003	0.12	1.26



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**

Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: September 10, 2010

Page: 2 of 3 **Part** 2

CERTIFICATE OF ANALYSIS

WHI10000348.1

	Method	7TD	7TD	7TD	7TD
	Analyte	Na	K	W	S
	Unit	%	%	%	%
	MDL	0.01	0.01	0.01	0.05
631951	Drill Core	<0.01	1.21	<0.01	1.94
631952	Drill Core	<0.01	0.35	<0.01	0.46
631953	Drill Core	<0.01	0.55	<0.01	0.98
631954	Drill Core	<0.01	0.36	<0.01	2.00
631955	Drill Core	<0.01	0.54	<0.01	12.38
631956	Drill Core	<0.01	0.05	<0.01	1.80
631957	Drill Core	<0.01	0.06	<0.01	1.71
631958	Drill Core	<0.01	0.28	<0.01	1.01
631959	Drill Core	<0.01	0.07	<0.01	1.13
631960	Drill Core	<0.01	0.21	<0.01	1.99
631961	Drill Core	<0.01	0.33	<0.01	2.57
631962	Drill Core	<0.01	0.50	<0.01	5.02
631963	Drill Core	<0.01	0.13	<0.01	2.51
631964	Drill Core	<0.01	0.27	<0.01	8.28
631965	Drill Core	<0.01	0.32	<0.01	5.80
631966	Drill Core	<0.01	0.30	<0.01	5.66
631967	Drill Core	<0.01	0.27	<0.01	1.95
631968	Drill Core	<0.01	0.38	<0.01	1.23
631969	Drill Core	<0.01	0.24	<0.01	1.12
631970	Drill Core	<0.01	0.02	<0.01	<0.05
631971	Drill Core	<0.01	0.28	<0.01	0.63
631972	Drill Core	<0.01	0.48	<0.01	1.61
631973	Drill Core	<0.01	0.51	<0.01	4.74
631974	Drill Core	<0.01	0.34	<0.01	1.10
631975	Drill Core	<0.01	0.60	<0.01	1.58
631976	Drill Core	<0.01	0.45	<0.01	1.76
631977	Drill Core	<0.01	0.19	<0.01	0.58
631978	Drill Core	<0.01	0.64	<0.01	1.65
631979	Drill Core	<0.01	0.66	<0.01	1.98
631980	Core Pulp	0.54	0.26	<0.01	2.02



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: September 10, 2010

Page: 3 of 3 **Part** 1

CERTIFICATE OF ANALYSIS

WHI10000348.1

	Method Analyte Unit MDL	WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD
		Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg
		kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%
		0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01
631981	Drill Core	2.21	0.008	0.015	0.09	1.11	3	0.023	<0.001	<0.01	2.50	<0.02	<0.01	0.004	<0.01	<0.01	5.02	1.24	0.009	0.20
631982	Drill Core	1.66	0.002	0.018	0.23	0.73	3	0.022	<0.001	0.01	2.93	<0.02	0.01	0.002	<0.01	<0.01	10.23	2.23	0.013	0.28
631983	Drill Core	2.44	<0.001	0.002	0.02	0.06	<2	0.002	<0.001	0.04	1.64	<0.02	0.02	<0.001	<0.01	<0.01	24.90	0.03	0.002	0.33
631984	Drill Core	2.93	<0.001	0.002	<0.02	<0.01	<2	0.005	<0.001	0.05	1.56	<0.02	0.02	<0.001	<0.01	<0.01	24.44	0.03	0.003	0.39
631985	Drill Core	2.77	0.004	0.006	0.04	0.12	<2	0.011	<0.001	0.04	3.23	<0.02	0.02	<0.001	<0.01	<0.01	19.28	1.37	0.008	0.30



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**

Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: September 10, 2010

Page: 3 of 3 Part 2

CERTIFICATE OF ANALYSIS

WHI10000348.1

	Method	7TD	7TD	7TD	7TD
	Analyte	Na	K	W	S
	Unit	%	%	%	%
	MDL	0.01	0.01	0.01	0.05
631981	Drill Core	<0.01	0.92	<0.01	3.00
631982	Drill Core	<0.01	1.59	<0.01	3.42
631983	Drill Core	<0.01	1.33	<0.01	1.74
631984	Drill Core	<0.01	1.95	<0.01	1.57
631985	Drill Core	<0.01	1.80	<0.01	3.54



Acme Analytical Laboratories (Vancouver) Ltd.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: **Selwyn Resources Ltd.**

Suite 700 - 509 Richards Street

Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: September 10, 2010

Page: 1 of 1 Part 1

QUALITY CONTROL REPORT

WHI10000348.1

	Method Analyte Unit MDL	WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD
		Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg	Al
		kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%	%
		0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01	0.01
Pulp Duplicates																					
631979	Drill Core	1.55	0.008	0.020	0.57	1.60	5	0.016	<0.001	<0.01	1.20	<0.02	<0.01	0.005	<0.01	<0.01	3.03	0.25	0.005	0.14	1.22
REP 631979	QC		0.008	0.021	0.58	1.65	6	0.017	<0.001	<0.01	1.28	<0.02	<0.01	0.005	<0.01	<0.01	3.09	0.26	0.005	0.14	1.24
Core Reject Duplicates																					
631951	Drill Core	1.28	0.004	0.010	<0.02	0.73	2	0.012	<0.001	<0.01	1.59	<0.02	<0.01	0.002	<0.01	<0.01	0.92	0.22	0.003	0.28	2.21
DUP 631951	QC		0.004	0.009	<0.02	0.69	<2	0.012	<0.001	<0.01	1.69	<0.02	<0.01	0.002	<0.01	<0.01	0.86	0.22	0.004	0.27	2.13
Reference Materials																					
STD OREAS131A	Standard		<0.001	0.033	1.74	2.93	32	0.003	0.002	0.18	5.84	<0.02	<0.01	0.008	<0.01	<0.01	5.37	0.07	0.002	3.20	4.72
STD OREAS131A	Standard		<0.001	0.032	1.71	2.87	32	0.002	0.002	0.18	5.81	<0.02	<0.01	0.008	<0.01	<0.01	5.24	0.06	0.002	3.08	4.56
STD R4T	Standard		0.063	0.512	1.55	3.47	89	0.350	0.040	0.09	23.81	<0.02	0.02	0.019	0.01	<0.01	2.21	0.05	0.013	1.42	3.96
STD R4T	Standard		0.065	0.531	1.67	3.55	92	0.363	0.044	0.10	24.87	<0.02	0.02	0.019	0.01	<0.01	2.28	0.06	0.019	1.43	3.90
STD R4T Expected			0.062	0.502	1.518	3.376	86	0.339	0.039	0.086	24.07	0.0087	0.0185	0.018	0.0138	0.0018	2.166	0.045	0.018	1.384	3.897
STD OREAS131A Expected			0.001	0.0322	1.72	2.83	30.9	0.0027	0.0023	0.1722	5.8166	0.0082	0.0028	0.0081	0.0047	0.001	5.286	0.0536	0.0025	3.1182	4.6057
BLK	Blank		<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	<0.01	<0.01	<0.02	<0.01	<0.001	<0.01	<0.01	<0.01	<0.01	<0.001	<0.01	<0.01
BLK	Blank		<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	<0.01	<0.01	<0.02	<0.01	<0.001	<0.01	<0.01	<0.01	<0.01	<0.001	<0.01	<0.01
Prep Wash																					
G1	Prep Blank		<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	0.08	2.46	<0.02	0.09	<0.001	<0.01	<0.01	2.57	0.09	<0.001	0.55	8.69
G1	Prep Blank		<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	0.08	2.39	<0.02	0.09	<0.001	<0.01	<0.01	2.53	0.09	0.001	0.56	8.73



Acme Analytical Laboratories (Vancouver) Ltd.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: **Selwyn Resources Ltd.**

Suite 700 - 509 Richards Street

Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: September 10, 2010

Page: 1 of 1 **Part** 2

QUALITY CONTROL REPORT

WHI10000348.1

		Method	7TD	7TD	7TD	7TD
		Analyte	Na	K	W	S
		Unit	%	%	%	%
		MDL	0.01	0.01	0.01	0.05
Pulp Duplicates						
631979	Drill Core		<0.01	0.66	<0.01	1.98
REP 631979	QC		<0.01	0.67	<0.01	2.05
Core Reject Duplicates						
631951	Drill Core		<0.01	1.21	<0.01	1.94
DUP 631951	QC		<0.01	1.17	<0.01	1.97
Reference Materials						
STD OREAS131A	Standard		0.15	3.44	<0.01	4.94
STD OREAS131A	Standard		0.15	3.33	<0.01	4.68
STD R4T	Standard		0.92	1.18	<0.01	15.64
STD R4T	Standard		0.95	1.21	<0.01	13.04
STD R4T Expected			0.9	1.153	0.00016	12.9903
STD OREAS131A Expected			0.1501	3.1584	0.0005	4.8
BLK	Blank		<0.01	<0.01	<0.01	<0.05
BLK	Blank		<0.01	<0.01	<0.01	<0.05
Prep Wash						
G1	Prep Blank		3.01	3.08	<0.01	<0.05
G1	Prep Blank		3.00	3.38	<0.01	<0.05



1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: Selwyn Resources Ltd.

Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Submitted By: Jason K. Dunning

Receiving Lab: Canada-Whitehorse

Received: August 30, 2010

Report Date: September 10, 2010

Page: 1 of 2

CERTIFICATE OF ANALYSIS

WHI10000347.1

CLIENT JOB INFORMATION

Project: Selwyn Project
Shipment ID:
P.O. Number: 1710-DON-198
Number of Samples: 29

SAMPLE PREPARATION AND ANALYTICAL PROCEDURES

Method Code	Number of Samples	Code Description	Test Wgt (g)	Report Status	Lab
R200-250	28	Crush split and pulverize 250g drill core to 200 mesh			WHI
7TD2	29	4 Acid digestion ICP-ES analysis.	0.5	Completed	VAN

SAMPLE DISPOSAL

STOR-PLP Store After 90 days Invoice for Storage
STOR-RJT Store After 90 days Invoice for Storage

ADDITIONAL COMMENTS

Acme does not accept responsibility for samples left at the laboratory after 90 days without prior written instructions for sample storage or return.

Invoice To: Selwyn Resources Ltd.
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6
Canada

CC:



This report supersedes all previous preliminary and final reports with this file number dated prior to the date on this certificate. Signature indicates final approval; preliminary reports are unsigned and should be used for reference only.
All results are considered the confidential property of the client. Acme assumes the liabilities for actual cost of analysis only.
** asterisk indicates that an analytical result could not be provided due to unusually high levels of interference from other elements.



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: September 10, 2010

Page: 2 of 2 Part 1

CERTIFICATE OF ANALYSIS

WHI10000347.1

	Method Analyte Unit MDL	WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD
		Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg	Al
		kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%	%
		0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01	0.01
631901	Drill Core	0.81	<0.001	0.006	0.08	<0.01	<2	0.011	<0.001	<0.01	1.19	<0.02	<0.01	<0.001	<0.01	<0.01	4.95	2.11	0.005	0.17	2.32
631902	Drill Core	0.43	<0.001	0.010	0.69	1.27	3	0.011	<0.001	<0.01	2.21	<0.02	<0.01	0.003	<0.01	<0.01	2.62	0.85	0.004	0.24	3.06
631903	Drill Core	1.68	<0.001	0.008	<0.02	0.12	<2	0.009	<0.001	0.04	1.17	<0.02	0.01	<0.001	<0.01	<0.01	16.49	1.07	0.004	0.21	1.83
631904	Drill Core	1.10	0.001	0.003	<0.02	0.20	3	0.007	<0.001	<0.01	0.62	<0.02	<0.01	<0.001	<0.01	<0.01	3.17	0.82	0.002	0.12	1.22
631905	Drill Core	1.87	0.003	0.008	0.91	3.69	3	0.010	<0.001	0.01	3.97	<0.02	<0.01	0.015	<0.01	<0.01	2.02	0.62	0.003	0.17	1.56
631906	Drill Core	11.84	0.002	0.007	0.33	2.69	<2	0.007	<0.001	0.01	2.27	<0.02	<0.01	0.008	<0.01	<0.01	2.75	0.11	0.001	0.09	0.76
631907	Drill Core	2.02	0.005	0.006	0.51	2.91	2	0.009	<0.001	0.02	1.80	<0.02	<0.01	0.008	<0.01	<0.01	2.93	0.07	0.001	0.12	1.22
631908	Drill Core	1.35	<0.001	0.003	0.28	0.81	<2	0.002	<0.001	0.06	0.62	<0.02	0.02	0.002	<0.01	<0.01	28.05	0.06	<0.001	0.11	0.25
631909	Drill Core	1.20	<0.001	0.003	0.54	1.92	<2	0.004	<0.001	0.04	2.14	<0.02	0.01	0.005	<0.01	<0.01	16.42	0.08	<0.001	0.10	0.57
631910	Drill Core	0.41	<0.001	0.005	0.73	2.90	<2	0.005	<0.001	0.03	1.59	<0.02	0.01	0.008	<0.01	<0.01	11.51	0.10	0.001	0.09	0.66
631911	Drill Core	0.56	<0.001	0.005	0.37	2.36	<2	0.005	<0.001	0.04	1.45	<0.02	0.01	0.006	<0.01	<0.01	14.34	0.10	0.001	0.10	0.70
631912	Drill Core	2.84	0.002	0.006	0.79	3.65	<2	0.007	<0.001	0.03	2.30	<0.02	<0.01	0.010	<0.01	<0.01	9.50	0.25	0.001	0.14	1.03
631913	Drill Core	2.73	0.003	0.010	1.34	0.89	4	0.007	<0.001	0.04	2.60	<0.02	0.01	0.003	<0.01	<0.01	15.78	0.43	0.002	0.21	0.53
631914	Drill Core	1.64	0.004	0.010	0.54	2.02	3	0.009	<0.001	0.03	2.67	<0.02	<0.01	0.006	<0.01	<0.01	10.57	0.41	0.003	0.11	0.80
631915	Drill Core	2.97	0.004	0.012	0.11	0.22	<2	0.007	<0.001	0.03	2.18	<0.02	0.01	<0.001	<0.01	<0.01	18.05	0.91	0.003	0.06	0.36
631916	Drill Core	1.83	0.002	0.005	0.03	0.06	<2	0.005	<0.001	0.03	0.93	<0.02	0.01	<0.001	<0.01	<0.01	21.95	0.18	0.002	0.06	0.21
631917	Drill Core	1.87	0.001	0.004	0.20	0.19	<2	0.004	<0.001	0.05	0.34	<0.02	0.02	<0.001	<0.01	<0.01	26.81	0.18	0.001	0.09	0.24
631918	Drill Core	2.48	0.003	0.006	0.15	0.81	3	0.007	<0.001	0.02	0.70	<0.02	0.01	0.002	<0.01	<0.01	17.97	0.50	0.002	0.09	0.59
631919	Drill Core	2.44	0.008	0.016	0.43	1.95	5	0.017	<0.001	0.01	1.54	<0.02	<0.01	0.005	<0.01	<0.01	5.56	0.43	0.004	0.16	1.40
631920	Drill Core	0.54	<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	0.02	0.12	<0.02	<0.01	<0.001	<0.01	<0.01	20.87	0.04	<0.001	11.04	0.11
631921	Drill Core	3.08	0.008	0.013	0.50	0.89	4	0.015	<0.001	0.01	2.73	<0.02	<0.01	0.003	<0.01	<0.01	5.95	0.27	0.004	0.14	1.22
631922	Drill Core	1.65	0.012	0.012	0.07	0.71	3	0.023	<0.001	<0.01	1.78	<0.02	<0.01	0.002	<0.01	<0.01	2.56	0.54	0.007	0.21	1.89
631923	Drill Core	1.59	0.009	0.016	0.10	0.92	3	0.021	<0.001	<0.01	2.70	<0.02	<0.01	0.003	<0.01	<0.01	4.07	0.77	0.006	0.18	1.58
631924	Drill Core	1.77	0.002	0.015	0.31	0.59	4	0.025	<0.001	<0.01	3.61	<0.02	0.01	0.002	<0.01	<0.01	10.27	3.11	0.017	0.20	2.07
631925	Drill Core	1.38	0.002	0.008	0.73	0.92	5	0.025	<0.001	<0.01	1.56	<0.02	0.01	0.003	<0.01	<0.01	10.37	3.38	0.017	0.23	2.32
631926	Drill Core	2.49	<0.001	0.003	0.04	0.04	<2	0.004	<0.001	0.03	2.46	<0.02	0.01	<0.001	<0.01	<0.01	16.99	0.07	0.004	0.37	3.13
631927	Drill Core	2.28	<0.001	0.002	<0.02	0.03	<2	0.003	<0.001	0.05	1.55	<0.02	0.02	<0.001	<0.01	<0.01	25.56	0.07	0.003	0.38	2.60
631928	Drill Core	1.35	0.002	0.002	<0.02	<0.01	<2	0.008	<0.001	0.04	2.28	<0.02	0.02	<0.001	<0.01	<0.01	21.18	0.03	0.003	0.30	2.87
631929	Core Pulp	0.06	0.002	0.856	0.97	1.31	226	0.002	0.002	0.23	2.80	<0.02	0.01	0.009	0.04	<0.01	2.03	0.02	0.002	0.12	1.33



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: September 10, 2010

Page: 2 of 2 **Part** 2

CERTIFICATE OF ANALYSIS

WHI10000347.1

	Method	7TD	7TD	7TD	7TD
	Analyte	Na	K	W	S
	Unit	%	%	%	%
	MDL	0.01	0.01	0.01	0.05
631901	Drill Core	0.01	1.64	<0.01	1.22
631902	Drill Core	0.02	2.14	<0.01	2.98
631903	Drill Core	0.01	1.29	<0.01	1.28
631904	Drill Core	<0.01	0.69	<0.01	0.63
631905	Drill Core	<0.01	0.80	<0.01	6.37
631906	Drill Core	<0.01	0.38	<0.01	3.85
631907	Drill Core	<0.01	0.69	<0.01	3.43
631908	Drill Core	<0.01	0.13	<0.01	1.10
631909	Drill Core	<0.01	0.27	<0.01	3.45
631910	Drill Core	<0.01	0.36	<0.01	3.35
631911	Drill Core	<0.01	0.36	<0.01	2.73
631912	Drill Core	<0.01	0.56	<0.01	4.58
631913	Drill Core	<0.01	0.17	<0.01	3.59
631914	Drill Core	<0.01	0.44	<0.01	4.18
631915	Drill Core	<0.01	0.17	<0.01	2.57
631916	Drill Core	<0.01	0.12	<0.01	1.00
631917	Drill Core	<0.01	0.13	<0.01	0.42
631918	Drill Core	<0.01	0.29	<0.01	1.09
631919	Drill Core	<0.01	0.77	<0.01	2.56
631920	Drill Core	0.01	0.03	<0.01	<0.05
631921	Drill Core	<0.01	0.66	<0.01	3.65
631922	Drill Core	<0.01	1.01	<0.01	2.24
631923	Drill Core	<0.01	0.87	<0.01	3.46
631924	Drill Core	<0.01	1.31	<0.01	4.54
631925	Drill Core	0.01	1.53	<0.01	2.14
631926	Drill Core	<0.01	2.06	<0.01	2.75
631927	Drill Core	<0.01	1.69	<0.01	1.67
631928	Drill Core	0.01	2.47	<0.01	2.50
631929	Core Pulp	0.58	0.27	<0.01	2.18



Acme Analytical Laboratories (Vancouver) Ltd.
1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: September 10, 2010

Page: 1 of 1 Part 1

QUALITY CONTROL REPORT

WHI10000347.1

	Method Analyte Unit MDL	WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD
		Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg	Al
		kg	%	%	%	%	gm/t	%	%	%	%	%	%	%	%	%	%	%	%	%	%
		0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01	0.01
Pulp Duplicates																					
631903	Drill Core	1.68	<0.001	0.008	<0.02	0.12	<2	0.009	<0.001	0.04	1.17	<0.02	0.01	<0.001	<0.01	<0.01	16.49	1.07	0.004	0.21	1.83
REP 631903	QC		<0.001	0.008	<0.02	0.12	2	0.010	<0.001	0.04	1.16	<0.02	0.01	<0.001	<0.01	<0.01	16.56	1.07	0.004	0.21	1.84
Core Reject Duplicates																					
631911	Drill Core	0.56	<0.001	0.005	0.37	2.36	<2	0.005	<0.001	0.04	1.45	<0.02	0.01	0.006	<0.01	<0.01	14.34	0.10	0.001	0.10	0.70
DUP 631911	QC		<0.001	0.005	0.38	2.39	<2	0.005	<0.001	0.04	1.47	<0.02	0.01	0.006	<0.01	<0.01	14.13	0.12	0.001	0.09	0.70
Reference Materials																					
STD OREAS131A	Standard		<0.001	0.033	1.74	2.93	32	0.003	0.002	0.18	5.84	<0.02	<0.01	0.008	<0.01	<0.01	5.37	0.07	0.002	3.20	4.72
STD R4T	Standard		0.063	0.512	1.55	3.47	89	0.350	0.040	0.09	23.81	<0.02	0.02	0.019	0.01	<0.01	2.21	0.05	0.013	1.42	3.96
STD R4T Expected			0.062	0.502	1.518	3.376	86	0.339	0.039	0.086	24.07	0.0087	0.0185	0.018	0.0138	0.0018	2.166	0.045	0.018	1.384	3.897
STD OREAS131A Expected			0.001	0.0322	1.72	2.83	30.9	0.0027	0.0023	0.1722	5.8166	0.0082	0.0028	0.0081	0.0047	0.001	5.286	0.0536	0.0025	3.1182	4.6057
BLK	Blank		<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	<0.01	<0.01	<0.02	<0.01	<0.001	<0.01	<0.01	<0.01	<0.01	<0.001	<0.01	<0.01
Prep Wash																					
G1	Prep Blank		<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	0.07	2.17	<0.02	0.07	<0.001	<0.01	<0.01	2.45	0.07	<0.001	0.59	7.10
G1	Prep Blank		<0.001	<0.001	<0.02	<0.01	2	<0.001	<0.001	0.07	2.20	<0.02	0.08	<0.001	<0.01	<0.01	2.49	0.08	<0.001	0.66	7.75



Acme Analytical Laboratories (Vancouver) Ltd.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: **Selwyn Resources Ltd.**

Suite 700 - 509 Richards Street

Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: September 10, 2010

Page: 1 of 1 **Part** 2

QUALITY CONTROL REPORT

WHI10000347.1

	Method	7TD	7TD	7TD	7TD
Analyte		Na	K	W	S
Unit		%	%	%	%
MDL		0.01	0.01	0.01	0.05
Pulp Duplicates					
631903	Drill Core	0.01	1.29	<0.01	1.28
REP 631903	QC	0.01	1.28	<0.01	1.27
Core Reject Duplicates					
631911	Drill Core	<0.01	0.36	<0.01	2.73
DUP 631911	QC	<0.01	0.36	<0.01	2.74
Reference Materials					
STD OREAS131A	Standard	0.15	3.44	<0.01	4.94
STD R4T	Standard	0.92	1.18	<0.01	15.64
STD R4T Expected		0.9	1.153	0.00016	12.9903
STD OREAS131A Expected		0.1501	3.1584	0.0005	4.8
BLK	Blank	<0.01	<0.01	<0.01	<0.05
Prep Wash					
G1	Prep Blank	2.84	3.19	<0.01	<0.05
G1	Prep Blank	2.76	3.09	<0.01	<0.05



1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: Selwyn Resources Ltd.

Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Submitted By: Jason K. Dunning

Receiving Lab: Canada-Whitehorse

Received: August 19, 2010

Report Date: September 02, 2010

Page: 1 of 3

CERTIFICATE OF ANALYSIS

WHI10000295.1

CLIENT JOB INFORMATION

Project: Selwyn Project
Shipment ID:
P.O. Number 1710-DON-182
Number of Samples: 34

SAMPLE DISPOSAL

STOR-PLP Store After 90 days Invoice for Storage
STOR-RJT Store After 90 days Invoice for Storage

Acme does not accept responsibility for samples left at the laboratory after 90 days without prior written instructions for sample storage or return.

Invoice To: Selwyn Resources Ltd.
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6
Canada

CC:

SAMPLE PREPARATION AND ANALYTICAL PROCEDURES

Method Code	Number of Samples	Code Description	Test Wgt (g)	Report Status	Lab
R200-250	34	Crush split and pulverize 250g drill core to 200 mesh			WHI
7TD2	34	4 Acid digestion ICP-ES analysis.	0.5	Completed	VAN
7TD.1	1	4 Acid digestion ICP-ES analysis	0.1	Completed	VAN

ADDITIONAL COMMENTS



This report supersedes all previous preliminary and final reports with this file number dated prior to the date on this certificate. Signature indicates final approval; preliminary reports are unsigned and should be used for reference only.
All results are considered the confidential property of the client. Acme assumes the liabilities for actual cost of analysis only.
** asterisk indicates that an analytical result could not be provided due to unusually high levels of interference from other elements.



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: September 02, 2010

Page: 2 of 3 Part 1

CERTIFICATE OF ANALYSIS

WHI10000295.1

	Method Analyte Unit MDL	WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD
		Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg	Al
		kg	%	%	%	%	gm/mt	%	%	%	%	%	%	%	%	%	%	%	%	%	%
		0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01	0.01
631851	Drill Core	0.66	<0.001	0.009	0.47	0.19	2	0.004	<0.001	0.03	3.86	<0.02	0.01	<0.001	<0.01	<0.01	17.74	0.13	0.002	0.16	0.67
631852	Drill Core	0.83	0.002	0.004	0.54	0.72	2	0.009	<0.001	<0.01	1.30	<0.02	<0.01	0.002	<0.01	<0.01	1.93	0.35	0.004	0.19	1.70
631853	Drill Core	2.06	<0.001	0.004	1.24	0.47	3	0.006	<0.001	<0.01	1.22	<0.02	<0.01	0.001	<0.01	<0.01	3.44	0.84	0.003	0.13	1.24
631854	Drill Core	1.70	0.002	0.004	0.03	0.24	<2	0.007	<0.001	0.02	1.06	<0.02	<0.01	<0.001	<0.01	<0.01	9.18	0.59	0.003	0.15	1.62
631855	Drill Core	0.97	0.002	0.007	1.08	10.52	2	0.005	<0.001	0.02	2.67	<0.02	<0.01	0.035	<0.01	<0.01	5.89	0.05	0.001	0.06	0.62
631856	Drill Core	2.13	0.003	0.011	4.07	16.19	5	0.008	<0.001	0.02	6.94	<0.02	<0.01	0.068	<0.01	<0.01	0.24	0.04	0.002	0.08	0.93
631857	Drill Core	1.92	0.004	0.007	1.46	5.30	3	0.009	<0.001	0.02	8.77	<0.02	<0.01	0.016	<0.01	<0.01	2.07	0.05	0.002	0.09	0.94
631858	Drill Core	1.95	0.003	0.006	2.53	6.51	2	0.007	<0.001	0.02	6.08	<0.02	<0.01	0.020	<0.01	<0.01	3.16	0.05	0.001	0.08	0.86
631859	Drill Core	0.90	0.002	0.004	2.49	4.77	2	0.006	<0.001	0.03	1.86	<0.02	<0.01	0.013	<0.01	<0.01	15.59	0.06	0.001	0.10	0.72
631860	Drill Core	0.99	0.001	0.002	0.22	1.17	<2	0.003	<0.001	0.03	0.88	<0.02	<0.01	0.003	<0.01	<0.01	13.54	0.04	<0.001	0.06	0.37
631861	Drill Core	0.96	0.001	0.002	0.13	0.82	<2	0.003	<0.001	0.02	1.00	<0.02	<0.01	0.002	<0.01	<0.01	10.46	0.04	0.001	0.05	0.37
631862	Drill Core	1.60	0.002	0.004	0.12	1.08	<2	0.006	<0.001	0.01	1.52	<0.02	<0.01	0.003	<0.01	<0.01	5.90	0.05	0.001	0.07	0.71
631863	Drill Core	1.65	0.008	0.005	0.16	0.81	<2	0.013	<0.001	<0.01	2.35	<0.02	<0.01	0.003	<0.01	<0.01	2.67	0.05	0.003	0.13	1.77
631864	Drill Core	0.39	0.006	0.016	4.53	10.79	4	0.011	<0.001	0.03	6.96	<0.02	<0.01	0.030	<0.01	<0.01	1.91	0.08	0.002	0.10	1.18
631865	Drill Core	1.58	<0.001	0.003	0.79	2.58	<2	0.003	<0.001	0.06	2.27	<0.02	0.01	0.009	<0.01	<0.01	26.88	0.05	<0.001	0.11	0.27
631866	Drill Core	1.68	0.002	0.004	1.81	5.77	<2	0.006	<0.001	0.03	2.19	<0.02	<0.01	0.018	<0.01	<0.01	13.12	0.07	0.001	0.20	0.80
631867	Drill Core	1.75	<0.001	0.003	>10	19.64	3	0.001	<0.001	0.02	0.97	<0.02	<0.01	0.103	<0.01	<0.01	8.51	0.03	<0.001	0.03	0.15
631868	Drill Core	0.71	<0.001	0.003	9.91	16.24	3	0.002	<0.001	0.02	0.50	<0.02	<0.01	0.089	<0.01	<0.01	15.43	0.02	<0.001	0.04	0.17
631869	Drill Core	1.13	0.001	0.004	1.01	1.62	<2	0.004	<0.001	0.03	1.75	<0.02	0.01	0.008	<0.01	<0.01	21.89	0.05	0.001	0.10	0.63
631870	Drill Core	0.87	0.001	0.002	1.80	2.47	<2	0.004	<0.001	0.03	1.94	<0.02	0.01	0.013	<0.01	<0.01	21.71	0.05	0.001	0.11	0.70
631871	Drill Core	2.08	0.002	0.006	0.07	0.19	<2	0.006	<0.001	0.03	2.72	<0.02	0.01	<0.001	<0.01	<0.01	19.18	0.06	0.002	0.13	0.89
631872	Drill Core	2.65	0.002	0.004	0.16	0.65	<2	0.006	<0.001	0.03	0.95	<0.02	0.01	0.002	<0.01	<0.01	18.10	0.06	0.001	0.10	0.73
631873	Drill Core	1.25	0.002	0.004	0.24	0.56	<2	0.005	<0.001	0.01	1.00	<0.02	<0.01	0.001	<0.01	<0.01	5.34	0.04	0.001	0.08	0.66
631874	Drill Core	1.82	0.002	0.008	1.04	1.06	2	0.008	<0.001	0.04	1.20	<0.02	0.01	0.002	<0.01	<0.01	18.85	0.20	0.002	0.13	0.76
631875	Drill Core	2.02	0.001	0.004	0.09	0.43	<2	0.004	<0.001	0.05	0.69	<0.02	0.02	0.001	<0.01	<0.01	26.27	0.17	<0.001	0.13	0.27
631876	Drill Core	1.98	0.004	0.013	0.21	1.05	<2	0.007	<0.001	0.03	1.31	<0.02	0.01	0.003	<0.01	<0.01	18.18	0.85	0.002	0.09	0.48
631877	Drill Core	2.09	0.006	0.016	0.26	1.66	<2	0.011	<0.001	0.02	1.36	<0.02	0.01	0.004	<0.01	<0.01	11.91	0.93	0.005	0.12	0.86
631878	Drill Core	2.12	0.003	0.005	0.17	0.80	<2	0.006	<0.001	0.02	0.79	<0.02	0.01	0.002	<0.01	<0.01	14.09	0.25	0.002	0.08	0.43
631879	Drill Core	1.12	0.004	0.013	0.44	2.17	3	0.010	<0.001	0.02	2.59	<0.02	<0.01	0.006	<0.01	<0.01	11.94	0.41	0.003	0.11	0.82
631880	Drill Core	0.93	0.004	0.009	0.27	1.47	3	0.009	<0.001	0.02	2.10	<0.02	0.01	0.004	<0.01	<0.01	11.75	0.39	0.003	0.10	0.74



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: September 02, 2010

Page: 2 of 3 **Part** 2

CERTIFICATE OF ANALYSIS

WHI10000295.1

Method	7TD	7TD	7TD	7TD	7TD.1
Analyte	Na	K	W	S	Pb
Unit	%	%	%	%	%
MDL	0.01	0.01	0.01	0.05	0.02
631851	Drill Core	<0.01	0.39	<0.01	4.97
631852	Drill Core	<0.01	0.96	<0.01	1.80
631853	Drill Core	<0.01	0.77	<0.01	1.51
631854	Drill Core	<0.01	1.09	<0.01	1.14
631855	Drill Core	<0.01	0.37	<0.01	8.70
631856	Drill Core	<0.01	0.53	<0.01	16.58
631857	Drill Core	<0.01	0.52	<0.01	13.05
631858	Drill Core	<0.01	0.51	<0.01	10.69
631859	Drill Core	<0.01	0.43	<0.01	5.03
631860	Drill Core	<0.01	0.20	<0.01	1.46
631861	Drill Core	<0.01	0.20	<0.01	1.41
631862	Drill Core	<0.01	0.41	<0.01	2.13
631863	Drill Core	<0.01	1.11	<0.01	2.99
631864	Drill Core	<0.01	0.68	<0.01	14.13
631865	Drill Core	<0.01	0.15	<0.01	4.25
631866	Drill Core	<0.01	0.34	<0.01	5.88
631867	Drill Core	<0.01	0.08	<0.01	12.29 10.21
631868	Drill Core	<0.01	0.09	<0.01	10.14
631869	Drill Core	<0.01	0.30	<0.01	3.00
631870	Drill Core	<0.01	0.35	<0.01	3.84
631871	Drill Core	<0.01	0.49	<0.01	3.41
631872	Drill Core	<0.01	0.42	<0.01	1.30
631873	Drill Core	<0.01	0.37	<0.01	1.21
631874	Drill Core	<0.01	0.41	<0.01	1.95
631875	Drill Core	<0.01	0.14	<0.01	0.93
631876	Drill Core	<0.01	0.28	<0.01	1.93
631877	Drill Core	<0.01	0.47	<0.01	2.33
631878	Drill Core	<0.01	0.24	<0.01	1.12
631879	Drill Core	<0.01	0.45	<0.01	4.15
631880	Drill Core	<0.01	0.41	<0.01	3.12



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: September 02, 2010

Page: 3 of 3 **Part** 1

CERTIFICATE OF ANALYSIS

WHI10000295.1

	Method	WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD
	Analyte	Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg
	Unit	kg	%	%	%	%	gm/mt	%	%	%	%	%	%	%	%	%	%	%	%	%
	MDL	0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01
631881	Drill Core	1.85	0.010	0.015	0.11	0.79	3	0.017	<0.001	0.01	1.88	<0.02	<0.01	0.002	<0.01	<0.01	6.66	0.18	0.004	0.16
631882	Drill Core	2.09	0.005	0.016	0.29	0.80	3	0.023	<0.001	<0.01	2.35	<0.02	<0.01	0.002	<0.01	<0.01	8.88	2.29	0.011	0.25
631883	Drill Core	2.64	0.001	0.003	0.05	0.08	<2	0.005	<0.001	0.04	1.86	<0.02	0.02	<0.001	<0.01	<0.01	24.16	0.09	0.003	0.37
631884	Drill Core	1.39	0.003	0.007	0.08	0.19	<2	0.010	<0.001	0.02	5.16	<0.02	0.03	<0.001	<0.01	<0.01	22.89	7.04	0.005	0.19



1020 Cordova St. East Vancouver BC V6A 4A3 Canada
Phone (604) 253-3158 Fax (604) 253-1716

Acme Analytical Laboratories (Vancouver) Ltd.

www.acmelab.com

Client: **Selwyn Resources Ltd.**
Suite 700 - 509 Richards Street
Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project
Report Date: September 02, 2010

Page: 3 of 3 **Part** 2

CERTIFICATE OF ANALYSIS

WHI10000295.1

	Method Analyte Unit MDL	7TD	7TD	7TD	7TD	7TD.1
		Na	K	W	S	Pb
		%	%	%	%	%
		0.01	0.01	0.01	0.05	0.02
631881	Drill Core	<0.01	0.79	<0.01	2.39	
631882	Drill Core	<0.01	1.33	<0.01	3.01	
631883	Drill Core	<0.01	1.48	<0.01	2.11	
631884	Drill Core	0.01	1.12	<0.01	6.06	



Acme Analytical Laboratories (Vancouver) Ltd.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: Selwyn Resources Ltd.

Suite 700 - 509 Richards Street

Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: September 02, 2010

Page: 1 of 1 Part 1

QUALITY CONTROL REPORT

WHI10000295.1

	Method Analyte Unit MDL	WGHT	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD	7TD
		Wgt	Mo	Cu	Pb	Zn	Ag	Ni	Co	Mn	Fe	As	Sr	Cd	Sb	Bi	Ca	P	Cr	Mg	Al
		kg	%	%	%	%	gm/mt	%	%	%	%	%	%	%	%	%	%	%	%	%	%
		0.01	0.001	0.001	0.02	0.01	2	0.001	0.001	0.01	0.01	0.02	0.01	0.001	0.01	0.01	0.01	0.01	0.001	0.01	0.01
Pulp Duplicates																					
631861	Drill Core	0.96	0.001	0.002	0.13	0.82	<2	0.003	<0.001	0.02	1.00	<0.02	<0.01	0.002	<0.01	<0.01	10.46	0.04	0.001	0.05	0.37
REP 631861	QC		0.001	0.002	0.13	0.84	<2	0.003	<0.001	0.02	1.02	<0.02	<0.01	0.002	<0.01	<0.01	10.67	0.04	<0.001	0.05	0.38
631867	Drill Core	1.75	<0.001	0.003	>10	19.64	3	0.001	<0.001	0.02	0.97	<0.02	<0.01	0.103	<0.01	<0.01	8.51	0.03	<0.001	0.03	0.15
REP 631867	QC																				
Core Reject Duplicates																					
631879	Drill Core	1.12	0.004	0.013	0.44	2.17	3	0.010	<0.001	0.02	2.59	<0.02	<0.01	0.006	<0.01	<0.01	11.94	0.41	0.003	0.11	0.82
DUP 631879	QC		0.004	0.013	0.43	2.19	4	0.009	<0.001	0.02	2.65	<0.02	0.01	0.006	<0.01	<0.01	12.18	0.42	0.003	0.11	0.83
Reference Materials																					
STD CCU-1C	Standard																				
STD CZN-3	Standard																				
STD OREAS131A	Standard		<0.001	0.033	1.79	2.90	32	0.002	0.002	0.17	5.94	<0.02	<0.01	0.008	<0.01	<0.01	5.48	0.06	0.002	3.16	4.73
STD OREAS131A	Standard		<0.001	0.032	1.75	2.94	32	0.003	0.002	0.17	5.91	<0.02	<0.01	0.008	<0.01	<0.01	5.48	0.06	0.002	3.19	4.75
STD PTC-1A	Standard																				
STD R4T	Standard		0.066	0.514	1.60	3.48	89	0.358	0.044	0.09	24.30	<0.02	0.02	0.019	0.02	<0.01	2.23	0.05	0.015	1.43	4.03
STD R4T	Standard		0.062	0.515	1.56	3.48	91	0.357	0.040	0.09	24.32	<0.02	0.02	0.019	<0.01	<0.01	2.27	0.04	0.016	1.44	3.96
STD SARM 71	Standard																				
STD R4T Expected			0.062	0.502	1.518	3.376	86	0.339	0.039	0.086	24.07	0.0087	0.0185	0.018	0.0138	0.0018	2.166	0.045	0.018	1.384	3.897
STD OREAS131A Expected			0.001	0.0322	1.72	2.83	30.9	0.0027	0.0023	0.1722	5.8166	0.0082	0.0028	0.0081	0.0047	0.001	5.286	0.0536	0.0025	3.1182	4.6057
STD CZN-3 Expected																					
STD CCU-1C Expected																					
STD PTC-1A Expected																					
BLK	Blank		<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	<0.01	<0.01	<0.02	<0.01	<0.001	<0.01	<0.01	<0.01	<0.01	<0.001	<0.01	<0.01
BLK	Blank		<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	<0.01	<0.01	<0.02	<0.01	<0.001	<0.01	<0.01	<0.01	<0.01	<0.001	<0.01	<0.01
BLK	Blank																				
Prep Wash																					
G1	Prep Blank		<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	0.08	2.30	<0.02	0.07	<0.001	<0.01	<0.01	2.28	0.08	<0.001	0.57	5.96
G1	Prep Blank		<0.001	<0.001	<0.02	<0.01	<2	<0.001	<0.001	0.08	2.37	<0.02	0.07	<0.001	<0.01	<0.01	2.39	0.08	<0.001	0.59	5.71



Acme Analytical Laboratories (Vancouver) Ltd.

1020 Cordova St. East Vancouver BC V6A 4A3 Canada

Phone (604) 253-3158 Fax (604) 253-1716

www.acmelab.com

Client: Selwyn Resources Ltd.

Suite 700 - 509 Richards Street

Vancouver BC V6B 2Z6 Canada

Project: Selwyn Project

Report Date: September 02, 2010

Page: 1 of 1 Part 2

QUALITY CONTROL REPORT

WHI10000295.1

Method		7TD	7TD	7TD	7TD	7TD.1
Analyte		Na	K	W	S	Pb
Unit		%	%	%	%	%
MDL		0.01	0.01	0.01	0.05	0.02
Pulp Duplicates						
631861	Drill Core	<0.01	0.20	<0.01	1.41	
REP 631861	QC	<0.01	0.20	<0.01	1.45	
631867	Drill Core	<0.01	0.08	<0.01	12.29	10.21
REP 631867	QC					10.18
Core Reject Duplicates						
631879	Drill Core	<0.01	0.45	<0.01	4.15	
DUP 631879	QC	<0.01	0.45	<0.01	4.22	
Reference Materials						
STD CCU-1C	Standard					0.39
STD CZN-3	Standard					0.11
STD OREAS131A	Standard	0.16	3.48	<0.01	4.96	
STD OREAS131A	Standard	0.16	3.46	<0.01	5.03	
STD PTC-1A	Standard					0.04
STD R4T	Standard	0.94	1.21	<0.01	15.79	
STD R4T	Standard	0.94	1.20	<0.01	15.04	
STD SARM 71	Standard					<0.02
STD R4T Expected		0.9	1.153	0.00016	12.9903	
STD OREAS131A Expected		0.1501	3.1584	0.0005	4.8	
STD CZN-3 Expected						0.113
STD CCU-1C Expected						0.34
STD PTC-1A Expected						0.05
BLK	Blank	<0.01	<0.01	<0.01	<0.05	
BLK	Blank	<0.01	<0.01	<0.01	<0.05	
BLK	Blank					<0.02
Prep Wash						
G1	Prep Blank	2.94	3.15	<0.01	<0.05	
G1	Prep Blank	2.93	3.06	<0.01	<0.05	